

REVIEW

[View Article Online](#)
[View Journal](#) | [View Issue](#)Cite this: *Polym. Chem.*, 2021, **12**, 29

PISA: construction of self-organized and self-assembled functional vesicular structures

Samuel Pearce ^a and Juan Perez-Mercader ^{*a,b}

The ability of living organisms such as cells and bacteria to create intricate and precise structures through the self-organization, segregation and assembly of their building blocks from simpler molecules found in their environment is vital for their morphologies and functions. The encapsulation of the essential ingredients for life within a semi-permeable membrane is widely accepted to have been a key event in the origin of life. Within this membrane a state far-from-equilibrium is maintained, which provides energetic conditions enabling complex functionalities such as adaptation and reproduction through internal metabolic processes. Polymerization-induced self-assembly (PISA) is a rapidly-developing method to produce polymersomes, or polymer vesicles, which can be considered as a synthetic analogy to vesicles with a lipid bilayer. Though to express the range of functions that systems that exhibit the basic functionalities of early life is indeed a challenge, PISA offers a particularly robust “boot up” mechanism which solves some of the challenges associated with the emergence of life. Recent advances in the exploitable chemistries applied to PISA expand the scope of complex nano-to-micron scale vesicular structures autonomously generated from a homogeneous mixture in mild conditions. This could ultimately lead to the achievement of synthesizing objects capable of mimicking basic behaviors and functions of natural life. Herein, we discuss the principles, syntheses and recent advances in the controlled formation of functional vesicle structures produced by PISA, while highlighting the exciting opportunities that can be explored in this emerging field.

Received 17th April 2020,
Accepted 18th August 2020

DOI: 10.1039/d0py00564a

rsc.li/polymers

1. Introduction

PISA can be viewed as a framework that uniquely integrates polymer chemistry and non-equilibrium physics into a unified controllable molecular environment where the above feed on one another. Its basic research and applications span many areas, from materials science or medicine, to autonomous and programmable materials and molecular soft-robots.¹ But given its capacity to implement the directed self-assembly of pre-designed self-organized molecular aggregates, PISA also opens new doors for the autonomous creation of biomimetic objects. We are used to seeing biological materials self-assemble into functional structures and systems with the ability to adapt by the acquisition of new functionalities to solve “problems” encountered by the living system, and therefore to evolve.^{2–4} Hence, among the most interesting basic functionalities that one may choose to implement are the ones shared by all extant living systems (LS), *i.e.*, functionalities that allow LS to (a) process information, (b) synthesize its own parts from

simpler components (for example, found in its environment), (c) self-reproduce and (d) evolve.^{2,5} Natural life as we know it of course uses biochemistry to implement the above. It comes as a nice surprise from PISA to see how non-biological chemistry is actually capable of generating rudimentary forms of basic functionalities provided by the architecture of natural living systems.

Indeed, one important and attractive feature of PISA is that it enables pathways for the synthesis of out-of-equilibrium chemical systems which (in at least a limited way) are capable of executing functions analogous to some that natural living systems carry out. In other words, PISA-generated systems can be designed to be artificial mimics of natural living systems¹²¹: they offer a great “chassis” on which to implement interesting chemistry-based and chemically-programmed functional architectures.

The generation of active vesicular structures from an initially homogeneous mixture of chemicals through their autonomous self-assembly during a controlled chemical reaction and without external intervention, as is done by PISA, actually solves one of the most fundamental issues in the development of functionality: the selective encapsulation of the required molecules in small volumes where they will not easily escape, and within which the action of the so-called

^aDepartment of Earth and Planetary Sciences and Origins of Life Initiative, Harvard University, Cambridge, MA 02138, USA. E-mail: jperezmercader@fas.harvard.edu^bSanta Fe Institute, Santa Fe, NM 87501, USA

chemical “arithmetic demon” can be greatly suppressed.^{6,7} This selective encapsulation increases the likelihood of chemical reactions and maintains the local concentration of their subsequent products by preventing their diffusion into the bulk solution. At the same time, it generates an important free-energy gradient between the inside of the vesicles and their environment.


PISA is a versatile process compatible with a variety of chemistries,⁸ which brings closer the creation of simple (vesicular) life-mimics in the lab and potentially bring us closer to understanding the (largely postulated^{9,10}) first steps that life on Earth may have taken in the form of protocells as it evolved from abiotic to biotic activity. Perhaps, in this way, PISA could also be used to inform the potential presence of life in other locations of the Universe where “life” (as we can imagine) may not be based on the biochemistry we see on Earth.

The formation of inanimate, *i.e.* not involving extant natural life and biochemistry, information-containing material structures by the self-assembly of simpler components is an extraordinary process to contemplate. This is so, perhaps, because in some sense these processes counter our common intuition, for we are used to seeing unassisted transitions usually proceeding from ordered states to less well-ordered states of matter.^{11,12} We know that PISA with its use of chemical fuels (monomers and activation reagents), dissipates energy, such as heat or light, to generate order. In fact, since

self-assembly in PISA refers to an out-of-equilibrium polymerization process where a chemical fuel is used, PISA provides an excellent vehicle and arena for the implementation of these processes with non-biochemical materials and for their use in the synthesis of autonomously controlled functional structures. Indeed, closer examination tells us that we only need to adjust our intuition to the fact that these “order generating” processes take place in dissipative systems, and that their nature is (or can be) mostly transient.

During dissipative processes, transient patterns or structures can form and re-organize. Given the appropriate conditions, this can be accompanied by the structure acquiring more forms of doing work and the generation (or deletion) of ways in which these patterns or structures and their internal components interact within or with their external environment to perform some kind of work. That is, new functions can be generated or destroyed during these processes. But self-organization and self-assembly in PISA are both dissipative processes in their nature and we can imagine that PISA could, with appropriate control, generate new functions.

To appreciate and identify the nature of the material processes that we have in mind, it is important to briefly recall some features of these two allied concepts: self-organization and self-assembly.¹³ Loosely speaking, these processes occur in sufficiently complex matter. Such processes usually involve a large number of individual molecules interacting in a coop-

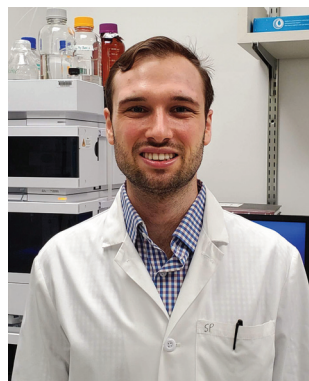

Samuel Pearce

Samuel Pearce received his MChem degree at the University of Sussex in 2014 and his Ph.D. at the University of Bristol, UK in February 2019. He joined the group of Dr Perez-Mercader at Harvard University in November 2019. His research interests encompass materials chemistry, nanoscience and self-assembly. His current research focuses on the development of polymerization-induced self-assembly systems to create artificial structures which behave in a similar manner to natural living systems.



Juan Perez-Mercader

Juan Perez-Mercader earned his Ph.D. in Physics from the City College of New York. A Profesor de Investigacion in Spain's National Research Council (CSIC), in 1998 he became the founding director of Spain's Centro de Astrobiologia in association with the NASA Astrobiology Institute. In 2010 he joined Harvard as a Senior Research Fellow in the Department of Earth and Planetary Sciences and Harvard Origins of Life Initiative. He is also an External Professor at the Santa Fe Institute. He has worked in many areas of Science, including Theoretical High Energy Physics, General Relativity, Non-equilibrium Processes, Self-organization, Complexity, Astrobiology and the development of In-situ Instrumentation for Life-Detection Outside the Earth. He was the architect of Spain's contribution to the NASA Mars Program and its participation in the Curiosity Rover. After joining Harvard his work has focused on understanding the practical role of chemistry and non-equilibrium physics in the emergence of life to generate in the laboratory ex novo synthetic artificial, non-biochemistry based forms of life. He is also active in the development of autonomous (native) chemical computation. (Picture Copyright, Harcourt Studio, Paris 2006.)



erative manner to produce ordered architectures at molecular and longer length scales. Self-organization is an out-of-equilibrium phenomenon, while self-assembly has been generally considered as the exclusive result of an equilibrium process. Specifically, self-organization is considered to be a dissipative, non-equilibrium generation of order at scales longer than the ones involving direct interactions among the self-organizing components or molecules. To maintain an ordered state, the injection or input of usable energy into the self-organized system is required. On the other hand, as noted above, self-assembly is generally understood as “a non-dissipative structural order” at a “macroscopic” level promoted by collective interactions taking place at the “microscopic level”.^{14–16} The latter interactions do not change the “character” of the components when they are integrated into the self-assembled structure, because chemical reactions are processes in which atoms and ions change partners with their attendant consequences, both in the structure and composition of matter and in the accompanying energy changes.^{17,18}


However there is a third logical possibility, which is seen in nature and plays a fundamental role in bringing together the self-organization and self-assembly of collective material structures. These phenomena fall under the class of Dissipative Self-Assembled (DSA) structures and correspond to material organizations combining self-organization and self-assembly *via* a dissipative process.¹⁴ These processes require a source of energy capable of producing the self-organizing components that would, eventually, self-assemble. However, these processes can also affect the energy landscape at the self-assembled scale and thereby make the self-assembly depend on the out-of-equilibrium conditions. DSA phenomena have a lot in common with the bases of metabolism in chemical biology but, significantly, they are not restricted to biochemistry.

We may think of this self-assembly process as controlled by the length of the amphiphile blocks as an order parameter in phase transitions:^{19,20} changing the order parameter changes the cooperative properties of the self-assembled objects/structures. This, of course, is well known and has been described by many authors^{3,21} who introduced the packing parameter, P , for the amphiphile as a “de facto” order parameter controlling the geometries attained by self-assembled amphiphiles.^{1,22,23} The packing parameter can be considered as a convenient rationalization of the relationship between the ratios of the amphiphilic moieties by volume and the observed morphologies. Thus we see how by changing the value of P , we can actually enact a sequence of interesting structures, including vesicles. However, it must be remembered that the free energy of the system determines the phenomena observed, of which the primary contributions are the degree of chain-stretching within the solvophobic region, the repulsive interactions between the solvophilic moieties such as steric or electrostatic repulsions, and the interfacial energy between the solvophobic region and solvent media.²⁴ In fact, it is here where PISA polymerization chemistry meets condensed matter physics and enables both the self-organized synthesis of amphiphiles and their self-assembly into structures. These, in turn evolve

in a morphology sequence controlled by the chemical nature of the PISA reaction and the environment into which it takes place. Furthermore, since chemical reactions can be thought of as events of molecular recognition²⁵ one can begin to envisage^{26–29} how PISA can potentially enable an extraordinary scenario for molecules recognizing molecules and use the sequences into which these molecules react to build material structures which can accomplish tasks or functions in a programmed fashion.

Prominent among the structures generated in PISA are the so-called polymersomes.³⁰ These are vesicular objects consisting of a polymer membrane enclosing a lumen. Before the advent of PISA, lipid-based vesicles (liposomes) and polymersomes have been studied and applied in many areas of science and technology, with applications ranging from studies of the origin of DNA/RNA-based life to medicine and cosmetics. Without PISA, the fabrication of vesicles is usually achieved using pre-prepared amphiphiles *via* numerous methods which involve careful physical tuning of the constituent parts and their environments. These multistep processes are by no means autonomous and include, but are not confined to, microfluidics, extrusion and solvent-switch techniques.³¹

The lumen of the PISA produced vesicles can in principle contain active chemical reactions, including instances of the PISA reaction itself, and the polymer membrane of the vesicle provides an already mentioned free-energy gradient between the lumen and the environment within which the vesicle exists. This membrane contains defects and is not perfectly impermeable which can allow materials to be exchanged between the lumen and the bulk solution. The size of these polymersomes ranges between 100's nm and 10's of microns, depending on the actual details of the PISA chemistry and of course the solvent in which the chemistry takes place. Once the vesicles form, the RAFT polymerization reaction goes on both inside and outside the vesicle. Monomers which make up the solvophobic contribution are therefore consumed at different rates and their concentration in both sides of the membrane will change. This generates a compensating change in the free-energy values and gradient generated when the vesicle assembly first took place. Superimposed on this is the hydrodynamic evolution of the vesicles.^{3,32,33} As a consequence of the above, there begin to appear new local and global minima for the free-energy which lead to changes in morphology. All this involves simultaneous interaction at different time and space scales and, therefore, provides a number (if not more) of new possibilities for the distribution and dissipation of the energy and entropy produced in the full (open and out-of-equilibrium) system. Depending on the detailed chemical nature of the reaction components, conditions and products, the essential gradient of free-energy keeps changing as the PISA reaction goes on and may generate conditions that lead to internal order within the PISA-generated structure. In other words, PISA can lead to new functionalities by the dynamical competition between internal and external components acting as vehicles to organize the interior of the, now evolving, initially generated structure.



Some protocell systems exist which exhibit complex functions related to natural life, including lipid-based vesicles capable of division³⁴ or systems based on coacervation³⁵ which are of substantial interest in origins of life scenarios. These include coacervates capable of maintaining concentration gradients through membrane formation (*via* the addition of amphiphilic molecules),³⁶ forming secondary structures³⁷ and promoting complex biological processes.³⁸ The introduction of PISA in protocell research has opened up a completely new set of scenarios, as the autonomous amphiphile synthesis and vesicular self-assembly provided by PISA addresses the significant challenge surrounding the property (b) mentioned above and offers a means for the autonomous transformation of external energy and chemical fuels into a system-level “boot-up”³⁹ solution from a homogeneous mixture to one of the chicken and egg problems in the origin of life: the “concentration” problem. The concentration of certain key chemicals inside a vesicle/compartiment can be substantially greater than in the surrounding solution. Thus, their probability of reacting increases and makes possible otherwise unlikely sequential chemical processing and synthesis due to the presence of the aforementioned “arithmetic demon”^{6,7} which plagues origins of life scenarios. Remarkably, besides generating functional vesicles with applications to many areas of science and technology, PISA has the potential to solve in a single shot the metabolism-first, information-first and “boot-up” process in the origin of life.^{40,41}

To explore the application of PISA for producing synthetic functional vesicles, this review is structured as follows: during this introduction we have discussed, in a qualitative way, some of the non-equilibrium aspects of PISA. To make the review somewhat self-contained, in section 2 we will briefly discuss the principles behind PISA, followed by section 3 where we will briefly touch on some relevant methods for producing vesicles by PISA. In section 4 we discuss PISA-produced vesicles which exhibit emergent phenomena and complex behavior. This is followed by a section on responsive and controllable vesicle architectures for some areas of PISA related research. We will end with section 6 where we offer some conclusions and a perspective outlook regarding the use of PISA to synthesize objects featuring intrinsic functionalities.

2. Principles behind polymerization-induced self-assembly

2.1. The significance of controlled polymerizations

To produce well-defined and controllable assemblies in solution, it is essential that the amphiphiles are consistent in nature. Living polymerization methods yield block copolymers of low polydispersity and controllable molecular weight, which act as well-defined amphiphilic building blocks. This has allowed for the systematic study of the solution-phase self-assembly of amphiphilic block copolymers.²⁴ In particular, controlled radical polymerizations such as nitroxide-mediated polymerization (NMP), atom transfer radical polymerization

(ATRP) and reversible addition–fragmentation chain-transfer (RAFT) polymerizations have provided robust protocols to produce block copolymers of controlled molecular weight and low polydispersity. Additionally, if the living character of the polymerization is maintained during PISA, consumption of monomeric reagents can continuously occur and keep the system in a state away from thermodynamic equilibrium.

2.2. Amphiphilic block copolymer solution-based self-assembly and the challenge of scale

In contrast to self-assembled constructs of molecular amphiphiles, in which the structures are highly dynamic and amphiphiles readily exchange between the structures and solution, structures comprising BCP amphiphiles are not labile with regards to the exchange of individual molecules.⁴² This means that the structures formed in solution by amphiphilic block copolymers are primarily under kinetic, rather than thermodynamic, control.⁴³ The traditional method of BCP self-assembly in solution involves an approach in which a pre-prepared BCP is molecularly dissolved, followed by a switch which results in the aggregation of the core-forming block, for instance by changing the pH or solvent conditions.⁴⁴ Eisenberg and coworkers published a series of important early reports of this process, in which BCPs with a short solvophilic block were used to produce a remarkable array of well-defined “crew cut” structures.⁴⁵

Considering the previously discussed packing parameter, in practical terms the obtained morphologies for a given BCP in solution are dependent on the relative solubility of the respective co-blocks and so changes in the solvent medium can drastically alter the morphology observed.⁴⁶ More recently the use of corona-forming blocks which exhibit variable solubility profiles dependent on conditions such as temperature or pH have been used to alter the effective packing parameter, which results in a switch between observed morphologies. This gives rise to a range of triggerable, dynamic behaviors of BCP vesicles following initial assembly. Due to the complexity of the solution-phase self-assembly behavior of BCPs and its dependence on concentration, post-polymerization solvent-switch methods are often carried out under highly dilute conditions (<1% w/w). Additionally, controlled BCP assemblies produced by the traditional approach are often difficult to replicate on a large scale, limiting their commercial potential.

2.3. Morphological evolution during PISA

Chain-extension of a solvophobic block from a solvophilic polymer using a controlled polymerization method in selective solvent media, results in the precipitation of the solvophobic block *in situ* to produce BCP aggregates in solution (provided that a critical length of the solvophobic chain is reached). This process is the driving force behind PISA, which produces consistent micellar architectures at relatively high concentration (typically between 10–50% w/w).^{47,48} Although a range of different controlled radical polymerization methods can be applied to the PISA process, it is RAFT polymerization that is the most prevalent method of choice.^{49,50}



In a standard PISA experiment, the degree of polymerization of the initial solvophilic block is pre-determined and so the solvophilic volume remains constant. Initial boot-up of the PISA process occurs by input of an energy stimulus which initiates the polymerization reaction and the consumption of monomer that forms the solvophobic block begins. During the polymerization of the solvophobic block, the free-energy-gradient is maintained as the continued polymerization keeps the system in a state far-from-equilibrium. During this process, the volume fraction of the solvophobic block continually increases until full conversion of monomer is achieved.³³ Mechanistic studies into the PISA process have shown that for a system in which vesicles are targeted, the observed morphologies evolve during polymerization according to the packing parameter, and the mean curvature of the structures is continually reduced *in situ* (Fig. 1A).⁵¹ At the point of aggregation, spherical micelles are obtained, which subsequently

fuse to form short worm-like micelle structures. Long, linear worm-like micelles are then formed but rapidly branch with multiple junction points. These junction points swell and merge, producing “octopi” structures. The bilayers reach a critical point during the polymerization and “wrap-up” to form jellyfish structures, which finally enclose the remaining worm-like micelles to form vesicles (Fig. 1A). Interestingly, Zhang and coworkers showed that this process can be reversed by the polymerization of a third solvophilic coblock from pre-formed vesicles, as the volume fraction of the solvophobic block is continuously reduced.⁵²

2.4. Morphological control and the construction of phase diagrams

Given that morphologies can be observed to change *in situ* during the PISA process, phase-pure BCP nanostructures can be targeted by careful control over the DPn of the core-forming

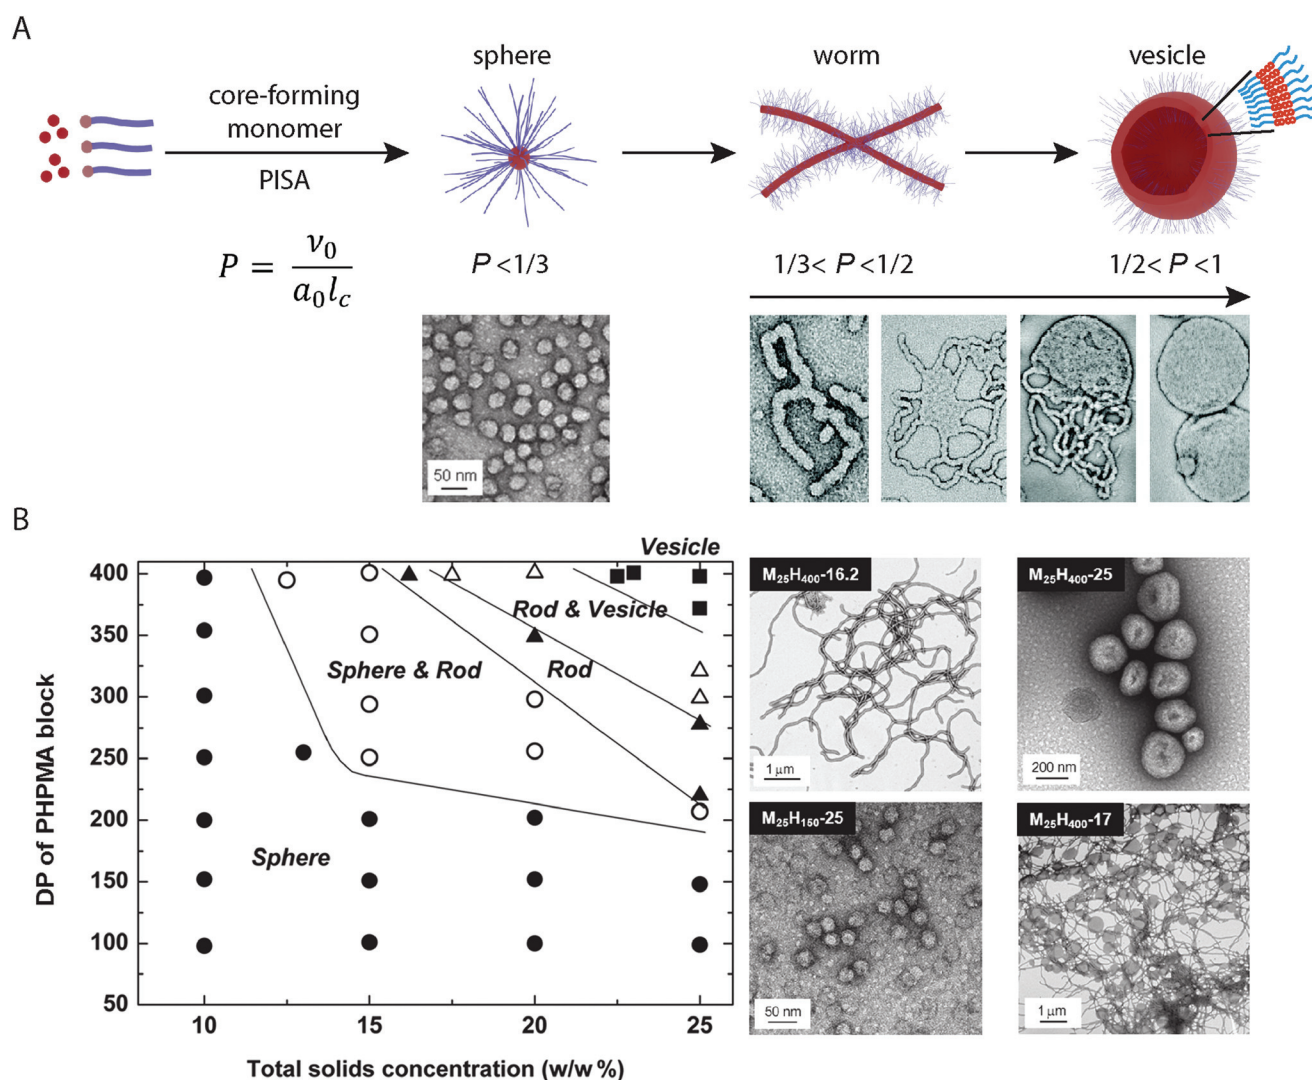


Fig. 1 (A) Basic mechanism of the structural evolution from spheres to vesicles during the PISA process. Adapted with permission from ref. 33 and 51. (B) Constructed morphological phase diagram for a poly(2-(methacryloyloxy)ethylphosphorylcholine) (PMPC)-*b*-PHPMA BCP in aqueous solution. Adapted with permission from ref. 33. Copyright 2011 American Chemical Society.



Though some degree of control over the vesicle size has been demonstrated, there are relatively few reports of using PISA to produce vesicles over multiple micron scales. To obtain structures through PISA relevant to artificial biology, such as artificial protocells, the ability to produce vesicles over the relevant length scales of 1–100 μm is essential. Such structures are termed giant vesicles (GVs) or giant unilamellar vesicles (GUVs).⁶² GV s have been produced by conventional BCP self-assembly protocols^{63,64} and PISA can also be applied to the formation of such structures. Yoshida published early examples of giant vesicles in a series of reports (Fig. 2C), dating back to 2013.⁶⁵ In this first example, UV-initiated NMP was used to produce a poly(methacrylic acid) (PMAA) stabilizing block in methanol, from which a poly(methyl methacrylate) (PMMA)-*r*-MAA random copolymer was polymerized in a MeOH/H₂O 3/1 v/v selective solvent mixture. SEM imaging showed the resulting giant vesicles to be relatively uniform, exhibiting an average diameter of 4.74 μm with a polydispersity index of 1.3.⁶⁵ The giant vesicles were sensitive to tempera-

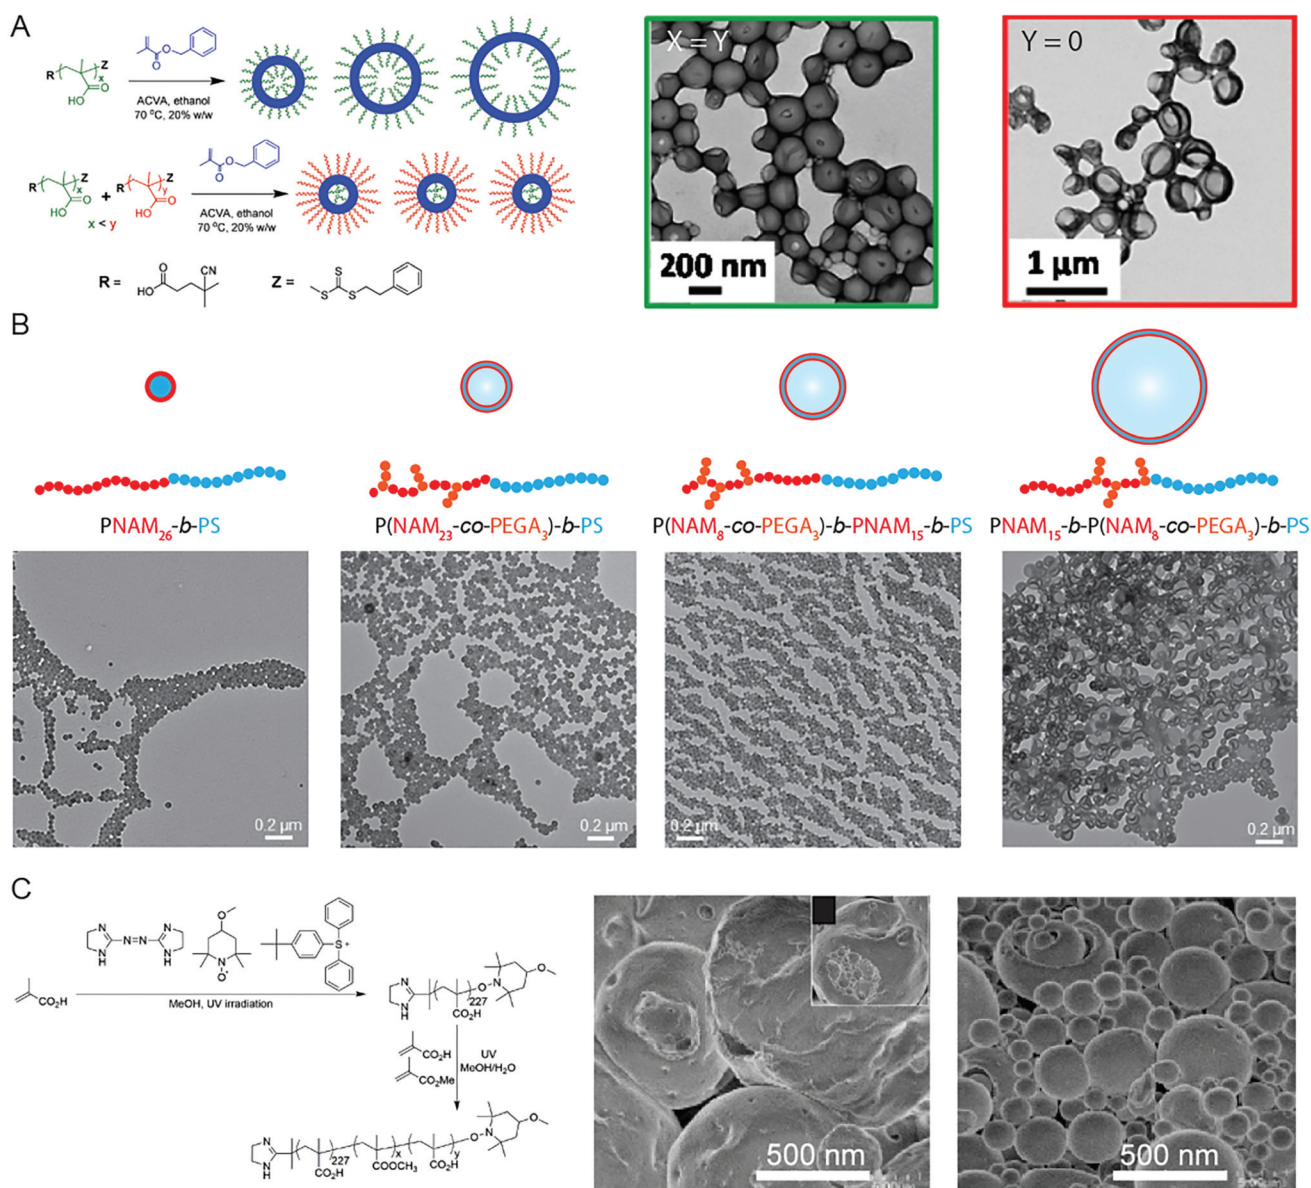


Fig. 2 (A) Control of vesicle size and uniformity by selection of the molecular weight and ratio of two mCTA reagents. Adapted with permission from ref. 59. Copyright 2014 American Chemical Society. (B) Vesicles of controlled size by manipulation of the mCTA topology and brush location. Adapted with permission from ref. 60. Copyright 2016 Wiley-VCH. (C) Giant vesicles comprising PAA-*b*-(PAA-*stat*-PMMA) produced by PISA in a methanol/water solvent system. Adapted with permission from ref. 66. Copyright 2014 Springer Nature.

ture, dissociating into small vesicles at 35 °C, followed by membrane and fiber-like aggregates at 40 °C.⁶⁵ Another report documented the contortion and subsequent fission of the giant vesicle morphology with increasing polymerization of the PMMA-*r*-PMAA core-forming block.⁶⁶ In all cases random copolymers comprising hydrophobic alkyl methacrylate and hydrophilic PMAA were used as the solvophobic cblock, which suggests that partial solvation of the core-forming block may be important to obtain the giant vesicle morphology.^{65,66}

GVs have been produced by photo-initiated RAFT PISA under aqueous dispersion conditions, in which the mechanism of growth could be analyzed *in situ* by optical and fluorescence microscopy.^{40,67} In contrast to previous reports of the

vesicle growth mechanism⁵⁸ the continued polymerization of HPMA from a PEG₄₃ mCTA resulted in the growth of giant vesicles of over 10 μm in diameter, until their eventual collapse. Associated with the variation of osmotic pressure each side of the membrane during irradiation with blue light, GV growth was driven by the influx of water through pore-defects, followed by the rapid expulsion of the lumen during collapse. This could occur in a cyclic manner, due to the presence of unreacted mCTA molecules and residual HPMA, observed as “phoenix” behavior: a name that underscores the property of these systems which experience growth, the collapse to start to grow and collapse again (sometimes for tens of cycles), as if it were from “their own ashes”.⁴⁰ The light-induced formation

acetyl acetone at room temperature. Aqueous dispersion polymerization of HPMA from a PEG trithiocarbonate CTA produced BCP objects ranging from spheres to vesicles.⁷⁶ This method could be used to load protein molecules into the vesicles *in situ*, utilizing the mild conditions under which PISA was conducted. Belousov-Zhabotinsky (BZ) redox oscillatory reactions have also been employed to initiate RAFT-PISA at room temperature, by the polymerization of butyl acrylate and acrylonitrile monomers from PEG-based mCTAs in the aqueous BZ reaction media.^{26,27,41}

3.2. Oxygen-tolerant systems for producing vesicles by PISA

As RAFT polymerizations rely on propagating radical species, most RAFT-based PISA protocols which use initiator molecules as radical sources are sensitive to oxygen and require thorough deoxygenation through nitrogen/argon displacement or multiple freeze–pump–thaw cycles. This can introduce limitation to the potential throughput and limit the scope of applications for vesicles produced using PISA-based protocols. Oxygen-tolerant living radical polymerizations have been the subject of intense interest in recent years⁷⁷ and similar protocols can be applied to RAFT-mediated PISA. Boyer and coworkers reported the use of a tris(bipyridine)ruthenium(II) chloride photoredox catalyst to activate the RAFT polymerization by photoinduced electron transfer (PET) under 460 nm light irradiation (Fig. 3A).⁷⁸ The continuous generation of radicals under irradiation allows for PISA without prior degassing of the solution,^{67,79} while also providing additional temporal control over the polymerization by “ON/OFF” irradiation of the catalyst. Other photoredox catalysts, *e.g.* 5,10,15,20-tetraphenyl21*H*,23*H*-porphine zinc (ZnTPP) can catalyze PET-RAFT under lower energy light irradiation to fabricate vesicles of various chemical composition by PISA.⁸⁰

An early example of redox-initiated polymerization to drive vesicle formation, involved the emulsion polymerization of butyl acrylate in aqueous media using cerium(IV) ions at 40 °C for 3 hours.⁸¹ Importantly, no prior treatment such as degassing or removal of inhibitors was required for the polymerization reaction to occur. In this reaction, the alcohol functional group of a PEG₃₄ macromolecule was activated by oxidation using the cerium(IV) ions, allowing for the radical polymerization of *n*-butyl acrylate to occur. Giant vesicles with an average diameter of 3.5 μm were obtained, in contrast to the nanoscale latex particles usually obtained by aqueous emulsion polymerizations. As mentioned previously, the redox oscillatory BZ reaction can be applied to PISA as a vehicle for using chemicals as a fuel to produce the radicals for RAFT polymerization.^{26,27,82} The BZ reaction consists of the oxidation of an organic species, typically malonic acid, by the bromate species of a strong acid, in the presence of a redox catalyst *e.g.* tris(bipyridine)ruthenium(II) chloride that can oscillate between two redox states. The radicals are sourced from the BrO₂* and the organic species, though studies suggest that it is the organic species specifically which initiates the polymerization (Fig. 3B).²⁶ The oscillatory nature of the reaction means that radicals are constantly generated, which

Alternatively, it is possible for redox processes to initiate PISA. Using hydrogen peroxide to activate the enzyme horseradish peroxidase, radicals were produced by oxidation of

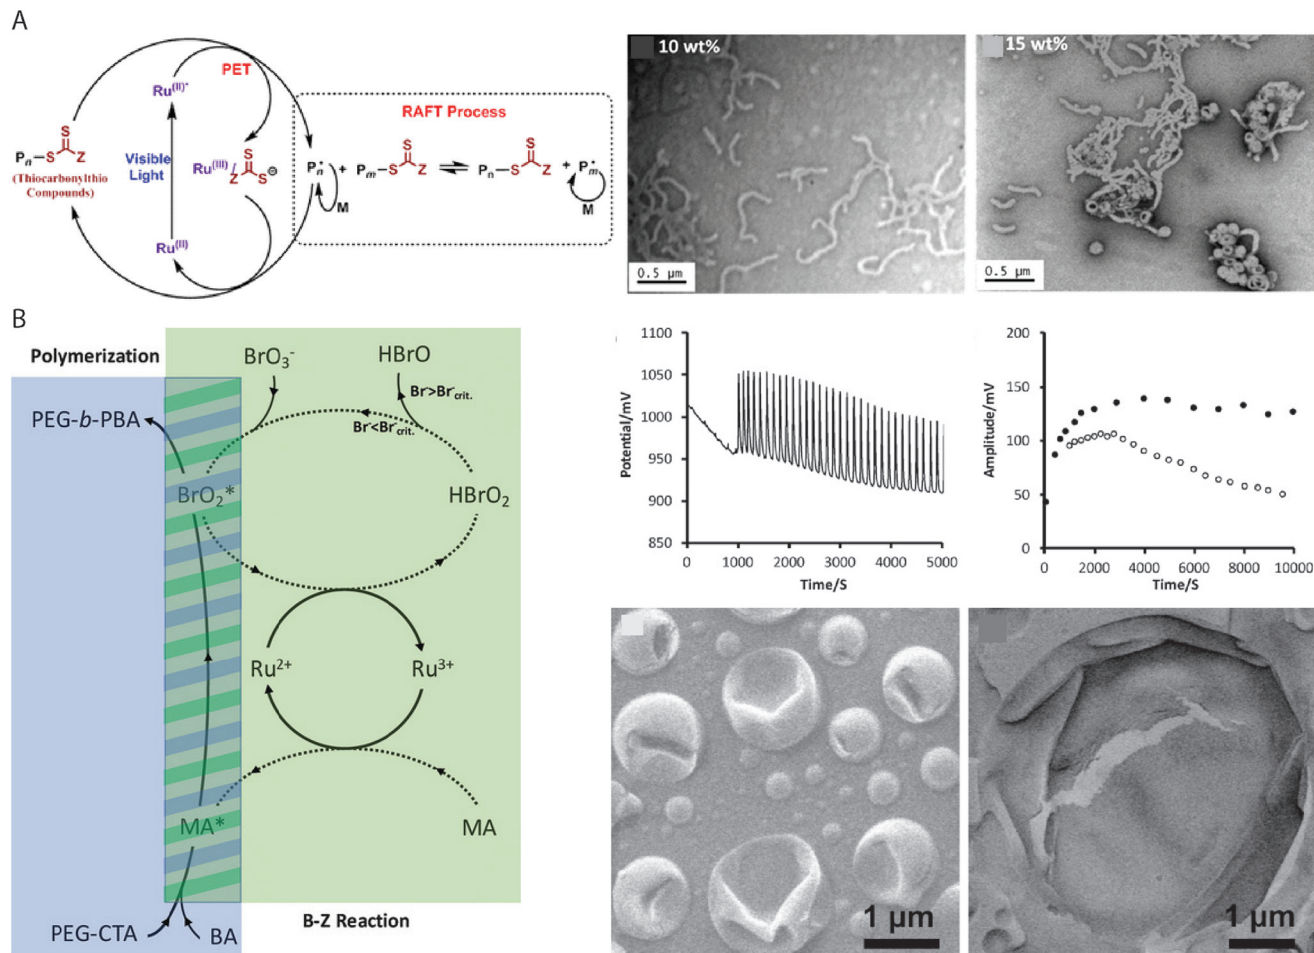


Fig. 3 (A) Proposed mechanism of ruthenium-catalyzed PET RAFT, with TEM images of the $\text{POEGMA}_n-b\text{-PBzMA}_m$ BCP structures produced by ethanolic PET-RAFT PISA at 10% and 15% w/w concentrations. Reproduced with permission from ref. 78. Copyright American Chemical Society 2015. (B) Mechanism of BZ-induced polymerization, producing BrO_2^* and organic radicals for polymerization. Oscillation profile of the BZ reaction, measured amplitude of redox oscillations and SEM images of the giant polymer vesicles. Reproduced with permission from ref. 26. Copyright 2017 Wiley-VCH.

results in “polymerization through” the oxygen in the system,⁸³ allowing the PISA reaction to be carried out under open-to-air conditions. Giant vesicles produced in the reaction entrap the oscillating chemical reaction, which can be used in chemical communication or as a chemical Turing machine.²⁵ Alternatively, a semibatch pH oscillator has been used to initiate RAFT PISA of BA τ a dithioester PEG mCTA.⁶⁹ The radicals produced by the bromate-sulfite pH oscillations at 40 °C initiated the aqueous dispersion polymerization, resulting in the formation of giant vesicles after an incubation time of *ca.* 150 min. The giant vesicles were observed to be dynamic in the system with budding and division events, which were attributed to the far-from-equilibrium state maintained by continuous addition of sulfite necessary to maintain the pH oscillations.⁶⁹

3.3. In-flow, high-throughput fabrication applied to PISA using thermal-, photo- and redox-initiated processes

PISA is an established method to obtain reproducible BCP assemblies on larger scales and at higher concentration than

post-polymerization BCP self-assembly approaches. Most PISA experiments are conducted in batch, which is not ideal for industrial applications or in the case of processes which rely on the system maintaining a state far-from equilibrium. In-flow PISA set ups have been reported using thermal-initiated RAFT polymerization to produce spheres, worms and vesicles in aqueous solution (Fig. 4A).⁸⁴ Warren and coworkers reported the sequential aqueous RAFT polymerization of dimethylacrylamide (DMAm), followed by diacetone acrylamide (DAAm) in the reactor yielded PDMAm-*b*-PDAAm BCP micelles on >100 g scales. It was observed that the polymerization rates were significantly higher in-flow compared to batch syntheses, attributed to the enhanced heat transfer to the polymerization solution in the tubular reaction. By careful control over the DP_n of the mCTA, solids concentration and residence time in the reactor, pure BCP vesicles could be obtained.⁸⁴

Continuous reactors for photo-initiated RAFT have been used to produce BCP structures from spherical micelles to vesicles by PISA. This approach was first reported by Boyer and co-



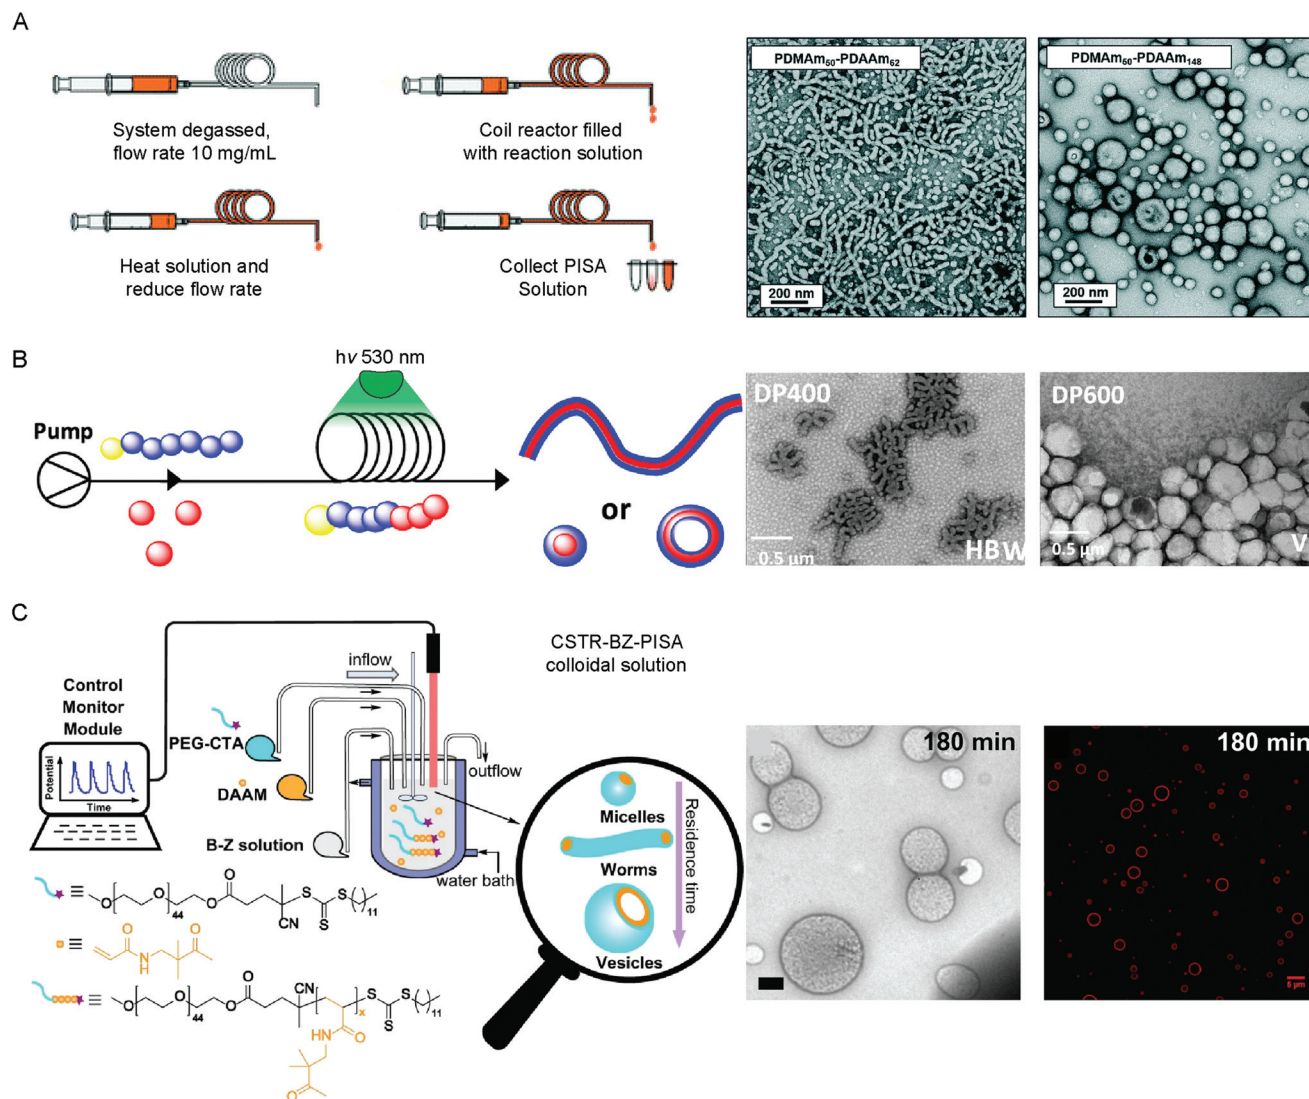


Fig. 4 Methods used to produce vesicles by PISA in flow by (A) thermal-initiated RAFT polymerization of DAAM from PDMAM₅₀ mCTA. Adapted with permission from ref. 84. Copyright 2019 Royal Society of Chemistry. (B) Photo-initiated PET-RAFT of diacetone-stat-dimethyl acrylamide from a PDMA trithiocarbonate mCTA. Reproduced with permission from ref. 86. Copyright 2019 American Chemical Society. (C) BZ-initiated PISA of DAAM from a PEG₄₄ trithiocarbonate mCTA using a CSTR in flow. Scale bar = 500 nm (TEM image) and 5 μm (fluorescence image). Reproduced with permission from ref. 29. Copyright 2019 Springer Nature.

workers, using a trithiocarbonate PEG mCTA to initiate the aqueous polymerization of HPMA under 460 nm light irradiation at 37 °C.⁸⁵ Excellent control over the obtained morphology of the BCP structures could be achieved by optimization of the residence time in the reactor, greatly increasing the scalability of the PISA process. To further expand this approach, BCP vesicles were produced through an air-tolerant PET-RAFT procedure using an Eosin Y/triethanol amine catalyst system for the aqueous dispersion polymerization of PDMAA-*b*-(poly(diacetone-stat-dimethyl acrylamide) PDMAA-*b*-(PDAAM-stat-PDMAA) copolymers using a trithiocarbonate CTA (Fig. 4B).⁸⁶ The flow reactor was set up to allow the initial polymerization of the PDMAA mCTA, before DAAM monomer was introduced to the system, following a pre-determined incubation time. The reduction in optical path lengths within the

tubular flow reactors allows for the uniform irradiation at higher intensity, accelerating the photo-controlled polymerization rate.⁸⁷ Recently, an alternative approach was reported using an air-tolerant in-flow PISA system based on the oscillatory BZ redox reaction (Fig. 4C).²⁹ A continuously stirred tank reactor (CSTR) was used to ensure the homogeneity of the BZ oscillations, such as the amplitude, periodicity and shape, preventing stationary space-periodic structures from occurring. Polymerization of DAAM from a trithiocarbonate PEG mCTA using BZ-RAFT-PISA yielded spherical micelles, worms, nano- and giant-sized vesicles, dependent on the residence time, BZ oscillation periodicity and the DP_n of the DAAM core-forming block. The continuous nature of the flow-chemistry meant that the state of the encapsulated BZ oscillations (*i.e.* the chemical properties) are known and can therefore be tuned.²⁹



4. Vesicles produced by PISA which exhibit emergent phenomena and complex behavior

4.1. Vesicle birth and death; phoenix and dye sensitive behavior of vesicles

Vesicles are formed in the last morphological transition during a conventional PISA process, after which the membrane continues to increase in thickness until a critical point is reached where the bilayer is no longer stable.⁵⁸ This does not mean that the vesicle morphology is not dynamic, as the continued consumption of the ingredients of the polymerization reaction maintain a “driving force” to keep the system in a far-from-equilibrium state.

Dynamic behavior of giant vesicles was observed during the $\text{Ru}(\text{bpy})_3^{2+}$ catalyzed photo-PISA of $\text{PEG}_{44}\text{-}b\text{-PHPMA}_n$ in aqueous media (Fig. 5A).^{40,67} Initial observation of the growth then collapse of giant vesicles between 8 hours 15 minutes and 13 hours 45 minutes reaction times during the polymerization reaction, was observed by Szymanski and Perez-Mercader using fluorescence microscopy (Fig. 5A).⁶⁷ This demonstrated that the far-from-equilibrium state of the system was maintained after giant vesicle formation. Giant vesicles of ca. 10 μm in diameter produced by photo-PISA could be easily imaged by optical fluorescence microscopy (Fig. 5A), using rhodamine 6G as a fluorescent probe. Additionally, the dynamic behavior of the structures due to the oxygen-tolerant polymerization of residual HPMa monomers under 450 nm light irradiation could be monitored. Acceleration of the giant vesicle growth


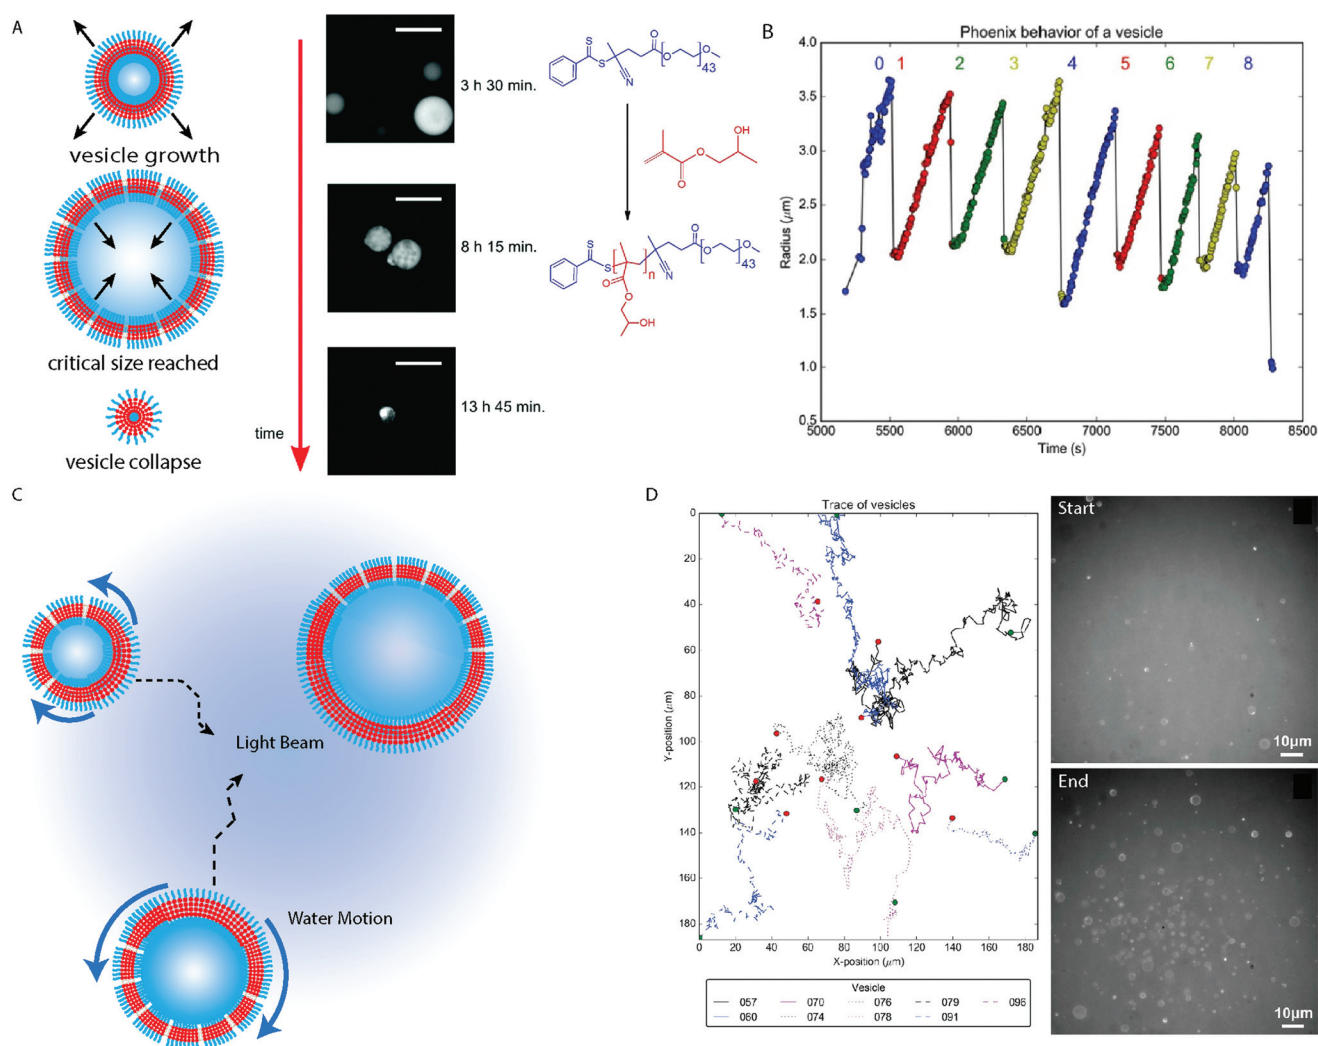


Fig. 5 (A) Cartoon depiction of $\text{PEG}\text{-}b\text{-PHPMA}$ vesicles with fluorescence microscopy images. Scale bars = 20 μm . Adapted with permission from ref. 67. Copyright 2016 Royal Society of Chemistry. (B) Trace displaying the change in polymersome radius when exposed to the blue light during microscopy analysis. Reproduced with permission from ref. 40. (C) Cartoon schematic depicting the Marangoni effect on vesicles formed by PISA under blue light irradiation used to activate the $\text{Ru}(\text{bpy})_3^{2+}$ PET-RAFT catalyst in a fluorescence microscope. (D) Path tracking of the BCP vesicles during the PISA experiment. $\text{PEG}\text{-}b\text{-PHPMA}$ vesicles before (top) and after (bottom) analysis of the phoenix behavior within the microscope. Reproduced with permission from ref. 40. Copyright 2017 Springer Nature.



was driven by the RAFT polymerization as the bilayer volume continually increased. During this growth period, the outer reaction solution enters the vesicle lumen through pore-defects in the vesicle membrane. The growth rate decays exponentially until a critical diameter is reached and local monomer depletion has occurred. The vesicle then reaches a maximum diameter at a critical point where the forces contributed by the membrane surface tension, the increase in core-forming polymer produced by the PISA process and the osmotic pressure between the vesicle interior and exterior become unbalanced, resulting in the rupture of the vesicle and its destructive collapse back into a droplet. This growth, collapse and regrowth of giant vesicles could occur multiple times in a process termed “phoenix” behavior (Fig. 5B).⁴⁰ The maximum diameter of the giant vesicles decreased following each cycle as material is continually consumed (Fig. 5B).⁴⁰ The mechanism behind “phoenix” behavior is currently not well understood, though subsequent studies found that judicious selection of the wavelength of the irradiated light, coupled with the appropriate fluorescent probe was important.⁶⁸ Merging of giant vesicles stained with rhodamine 6G was observed at higher solids concentration under 540–590 nm irradiation, demonstrating the transient nature of these structures in a non-equilibrium state.

Another interesting phenomena observed during the *in situ* microscopy analysis was the population growth of the phoenix vesicles observed during the experiment.⁴⁰ To this there are two contributions: firstly, phototaxis of the giant vesicles towards the area under blue light irradiation from the surrounding regions (Fig. 5C and D). Irradiation of a specific area with blue light in the fluorescence microscope results in a reaction gradient and consumption rate of the constituent molecules, as the polymerization reaction is most efficient within the beam center, which decreases with the light intensity towards the surrounding area. In the absence of blue light irradiation, the vesicles move randomly due to Brownian motion. The reason for the phototaxis of the objects can be rationalized by the Marangoni effect, as tension is induced within the membrane of the vesicle due to the vesicle surface closest to the center of the beam experiencing a greater rate of reaction. This creates anisotropy across the membrane of the vesicle, as the regions experiencing the fastest reaction have the greatest volume of polymer within the membrane and so have a lower surface tension (Fig. 5C). The surface tension gradient within the vesicle membrane results in aqueous solution moving from the region of lowest surface tension nearest the beam center, to the region of higher surface tension, where the membrane is thinner and has a greater defect density. This produces currents within the vesicles aqueous environment pushing the giant vesicles towards the area of highest light intensity.⁴⁰

The second contribution to the population growth is contributed by the conversion of droplets comprising mainly HPMA monomers stabilized by PEG-*b*-PHPMA amphiphiles to GVs.⁴⁰ Consumption of the HPMA monomer in the beam causes a modest increase in objects, until the RAFT polymeriz-

ation undergoes an exponential phase in HPMA consumption, resulting in a sharp increase in the vesicle population which continues in a non-linear manner. As the PEG mCTA and HPMA monomer are consumed by the PISA process, the rate of population growth slows and the system reaches a maximum vesicle population number. Thus it was observed that, due to the reaction gradient across the beam, a cumulative effect of monomer droplet to vesicle morphological evolution and the Marangoni-driven phototaxis of the giant vesicles to the beam center results in the dynamical phase transition observed during the analysis.⁴⁰ Currently, there are many aspects to these behaviors which are unknown and need to be explored, which is the subject of ongoing investigation by our group. In principle, a parallel between the behavior exhibited by this system can be drawn with some aspects of a proto-living system, such as the spontaneous formation of a membrane from a chemically active homogenous media, metabolism and possible forms of self-replication and system selection.

4.2. Vesicle division

Living cells exist in a non-equilibrium steady state or homeostasis and the interaction between their semi-permeable membranes is of critical importance for the transfer of chemical information and biological processes involved in cellular replication. To this end, the division of polymersomes produced by PISA would further demonstrate its applicability for protolife research. Vesicles comprising PEG-*b*-poly(acrylonitrile) (PAN) produced by the chemically oscillating BZ reaction were observed to grow, bud then divide during the PISA process.²⁷ The vesicle reproduction initially appeared as a smaller bleb on the side of the parent vesicle, which separates upon reaching a critical size, visualized by SEM imaging.²⁷ PEG-*b*-PBA vesicles produced by PISA initiated by a chemically-fuelled pH oscillator also exhibited similar behavior.⁶⁹ The nature of the oscillatory systems means that far-from-equilibrium conditions are maintained, and so the chemical environment within the interior lumen of the vesicle will be different to the outer medium, therefore chemical gradients and varying reaction rates compromises the membrane stability and so emergent phenomena result.

4.3. Multi-compartment vesicles for synthetic cell-like structures

Compartmentalization is a vital aspect of the structure of eukaryotic cells for their functionality, allowing for chemical reactions and gradients to be maintained. PISA can be used to fabricate multicompartment BCP assemblies using a variety of strategies. Framboidal compartmentalized vesicles have been produced by a “seeded” RAFT-PISA approach,⁸⁸ which involved the polymerization of a third coblock, BzMA, from pre-assembled PGMA-*b*-PHPMA diBCP assemblies. The immiscibility between PHPMA and PBzMA resulted in the formation of PBzMA nanodomains within the wall of the vesicle, which increased in size with increasing DPn.⁸⁸ A subsequent report showed that this strategy could be employed to produce pH-



5. Responsive and controllable vesicle structures for applied research

5.1. Functionalizable and cross-linkable vesicles

As the field of PISA matures, more strategies for its application in the synthesis of “smart” structures which respond to changes in environment, or exhibit stimuli-dependent functions have emerged in recent years.⁷¹ Living cells are capable of emergent behavior such as adaptivity, self-regulation, self-replication, contortion and motion, which are reliant on a multitude of complex chemical process occurring in a coherent manner. There are relatively few examples of the utilization of PISA to produce vesicles with adaptive or self-regulatory properties, though reports featuring vesicles capable of increasingly complex functions are emerging.⁹⁶

While the composition of BCP vesicles is less transient in comparison to small molecule or lipid bilayer-based analogues, the vesicle structure will degrade, or dissolution of the structures will result, following changes in conditions such as solvent composition, addition of surfactants or pH, in the absence of full life-like behaviors.⁹⁷ The self-assembled BCP morphology can be made resilient to such stresses through intra-core cross-linking, which can be performed *in situ* or using multi-pot post-polymerization techniques. For a detailed summary of the cross-linkage of BCP assemblies produced by PISA, the reader is referred to a recent perspective by Armes, Boyer and coworkers, particularly for the cross-linking of worm-like micelles.⁷¹ Herein an overview of the primary strategies associated with crosslinking BCP vesicles is discussed. Post-polymerization strategies usually involve a 2-step process which consists of the PISA synthesis of the vesicular structures, followed by an additional procedure to induce cross-linking. Chemical cross-linking by covalent bonds can be easily achieved by introducing appropriate functionality within the vesicle core. For instance, vesicles with a poly(glycidyl methacrylate) (PGlyMA) core-forming block can be easily cross-linked by a range of bifunctional nucleophilic reagents. This approach was used by Chambon, Armes and coworkers, by preparing vesicles comprising PGMA₅₅-(PHPMA₂₄₇-*stat*-PGlyMA₈₂) which were subsequently cross-linked using several reagents with terminal amine functional groups.⁹⁸ This allowed the vesicles to maintain their structural integrity in the presence

The *in situ* cross-linking of vesicles is possible using bifunctional divinyl monomers, although this can be challenging as cross-linkage can compete with the primary polymerization reaction. An and coworkers avoided this issue by using an asymmetric cross-linker, allyl acrylamide, which exhibited two different vinyl reactivities.¹⁰³ This resulted in the less reactive vinyl group incurring cross-linking at the latter stages of polymerization, producing vesicles with up to 5 mol% loading of cross-linkable monomer. Subsequently, it was reported that these vesicles could seed the continued polymerization of a third hydrophilic block, providing enhanced colloidal stability to the cross-linked structures.¹⁰⁴ A similar principle can be applied to symmetric cross-linkers,¹⁰⁵ through the copolymerization of 2-(diisopropylamino)ethyl methacrylate (DIPEMA) and cystamine-bismethacrylamide (CBMA) using a dithioester PEG macro-CTA. As the vinyl groups of the cross-linker are less reactive to the polymerization than the DIPEMA monomer, cross-linking was delayed to the latter stages of polymerization, allowing for controlled polymerization to occur beforehand.¹⁰⁵ It is important to note that while interesting for applications and for the extension of functionality of PISA-produced objects, techniques involving the covalent post-polymerization cross-linking of vesicles require multiple processes and are not achieved from homogenous solution in a 1-pot technique as most other PISA syntheses are conducted.

The response rate can be increased by using a pH-responsive coblock, for instance Guragain and Perez-Mercader produced vesicles by aqueous photoRAFT PISA comprising PEG₁₇-*b*-PDMAEMA₄₅-*b*-PHPMA₇.¹⁰⁸ The central PDMAEMA coblock is protonated during initial polymerization of HPMA monomer at pH 3.5. Micelle-to-worm/vesicle transitions were observed upon increasing the pH to 8, which was attributed to decreased solubility of the neutral PDMAEMA central block and loss of electrostatic repulsion between monomer units.¹⁰⁸ Zhang and coworkers produced vesicles comprising PPEGMA₉-*b*-(PDMAEMA_{40/80}-*co*-PHPMA₂₀₀) by photoPISA at 25 °C, which were sensitive to the bubbling of CO₂ through the aqueous solution.¹⁰⁹ This caused a decrease in the solution pH as the CO₂ dissolved to form carbonic acid, which protonated the PDMAEMA repeating units increasing the hydrophilicity of the core-forming block, resulting in the complete dissolution of the vesicle structures into polymer chains. In another example of using a weakly basic repeating unit in the polymer micelle core, Mable *et al.* reported rapid pH-triggered morphological transitions exhibited by PGMA-*b*-PHPMA-*b*-PDPA (DPA = 2-(diisopropylamino)ethyl methacrylate) framboidal vesicles at pH = 8.⁸⁹ The PDPA coblock is hydrophobic at high pH, resulting in colloidally-stable framboidal vesicles being produced. Once the pH was lowered to pH = 3, the PDPA block is rapidly protonated, resulting in dissolution of the vesicles, which was observed by the previously turbid solution becoming clear following acidification.⁸⁹ Time resolved SAXS analysis of the vesicle following acidification showed that the vesicle structures dissolved within 1 second, with the swelling of the bilayer observed within 50 ms. To prevent vesicle dissolution upon an environmental change, core cross-linking can be utilized, as discussed previously. Pan and coworkers produced PEG₁₁₃-*b*-PDPA₉₀ vesicles cross-linked by a divinyl monomer CBMA which exhibited reversible pH responsivity.¹⁰⁵ The average diameter of the vesicles was 320 nm at pH = 8, which increased to 560 nm at pH = 4, due to swelling of the core-

Vesicles formed by PISA which are sensitive to alternative stimuli other than pH and temperature have also been produced. Deng, Armes and coworkers used dynamic covalent chemistry to trigger vesicle-to-worm structural transition of PGMA₄₅-*b*-PHPMA_{*n*} vesicles, by reaction of the alcohol functional groups on the PGMA block with 3-aminophenylboronic acid (APBA) under aqueous conditions at pH = 10.¹¹¹ The formation of phenylborate ester groups along the hydrophilic PGMA polymer chains increases their effective volume, causing the structural transition to occur. The vesicle lumens were pre-loaded with silica nanoparticles, which could be released from the interior into the bulk solution upon addition of APBA. Faster release kinetics of the silica nanoparticles were observed at higher pH or APBA concentrations.¹¹¹ This method also worked with vesicles which possessed a longer PHPMA block of 300 repeating units, which did not previously exhibit thermal sensitivity, extending the scope for vesicles as a delivery vector.¹¹¹ UV light has been used to trigger worm-vesicle structural transitions by including UV-sensitive azo-groups within the hydrophobic segment.⁵⁷ PDMA₃₂-*b*-P(BzMA₆₀-*co*-AzoMA₆) (AzoMA = 4-phenyl-azophenyl methacrylate) worms-like micelles were initially produced by thermal RAFT PISA in ethanol at 15% w/w, then were subsequently diluted to 0.5% w/w. After UV irradiation for 1 h, vesicles structures were observed, due to the *trans*-*cis* conversion of the azo groups. This process could be reversed and the vesicles were

Cheng and Perez-Mercader produced vesicles with switchable porosity under temporal control using UV-light by using a PEG macroCTA functionalized with an azo-benzene group to initiate photo RAFT of HPMA under aqueous dispersion con-

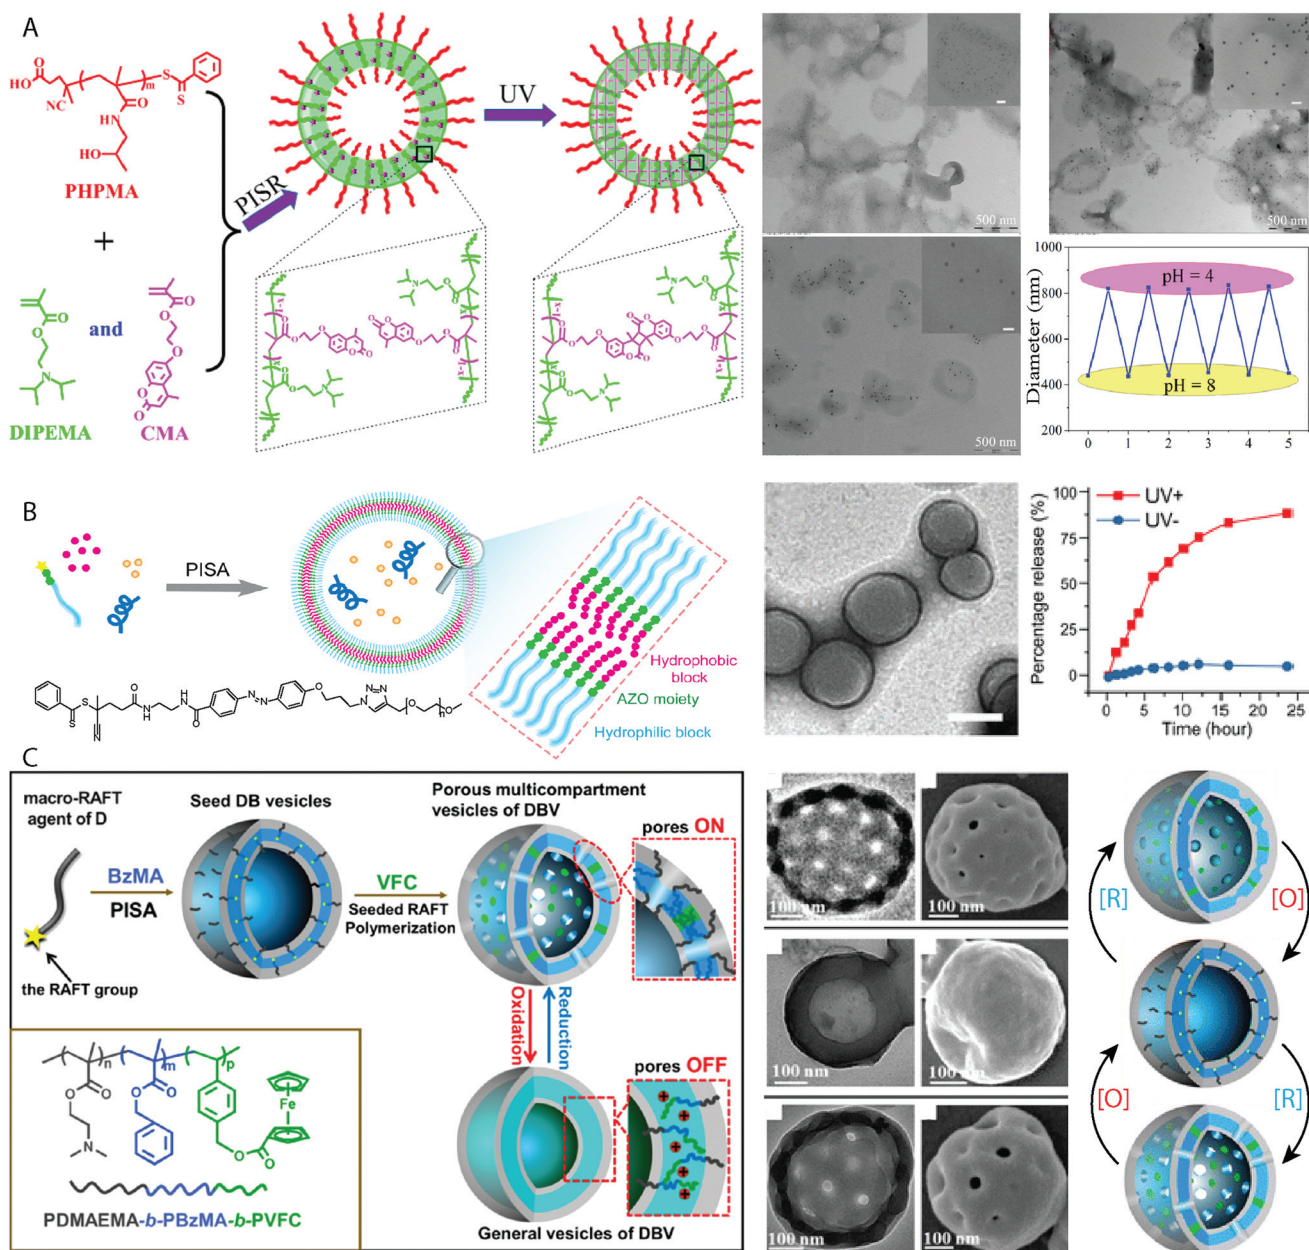


Fig. 6 (A) UV cross-linked PHPMA-*b*-(DIPEMA-co-PCMA) vesicles with controllable porosity exemplified by the selective uptake of Au nanoparticles of 5 nm, 10 nm and 15 nm diameters respectively. TEM images and graph depicting the reversible increase and decrease in vesicle diameter following cyclic reduction and increase in pH. Adapted with permission from ref. 112. Copyright 2017 American Chemical Society. (B) Vesicles which exhibit UV-switchable pores using an azo-benzene linker between the hydrophilic PEG and hydrophobic PHPMA block, with TEM images displaying the vesicle morphology and graph displaying the release of rhodamine 6G during UV irradiation. Scale bar = 200 nm. Adapted with permission from ref. 114. Copyright 2019 American Chemical Society. (C) Vesicles with redox-switchable pores by reversible chemical oxidation and reduction of a ferrocene-functionalized copolymer. Scale bars = 100 nm. Adapted with permission from ref. 115. Copyright 2015 American Chemical Society.

ditions (Fig. 6B).¹¹⁴ The UV-activated switch between the *cis* and *trans* isomers of the azobenzene functional group opened and closed pores in the vesicle membrane. Repeated photo-switching of the PEG-*b*-PHPMA vesicles was observed by UV-vis spectroscopy, with no degradation of the vesicular morphology observed by TEM and DLS analysis. Loading of the vesicle with a dye molecule, rhodamine 6G and macromolecular FTIC-dextran showed the selective release of rhodamine 6G upon

UV irradiation with no detectable release FTIC-dextran.¹¹⁴ FTIC-dextran release was achieved by exploiting the chemosensitivity of the azo group through cleavage using sodium dithionite. This resulted in irreversible disassembly of the vesicles and release of their interior lumen contents. Shi and Zhang achieved the synthesis of pore-switchable vesicles under redox control by using a two-step PISA-based protocol (Fig. 6C).¹¹⁵ Initially vesicles comprising PDMAEMA₃₅-*b*-PBzMA₂₇₄ were



catalyst produce a local electron-rich environment. The highly reactive electron species can push (or force) chemical reactions and processes, providing further internal osmotic instabilities favoring anisotropy in amphiphile packing and hence increase local defects. Vesicle collapse upon reaching a critical state can allow the system to reduce its free energy, release accumulated high energy chemical species and refresh the cycle. Through these contributions, an albeit simplified, parallel between PISA systems and natural processes governing function can be drawn. Further investigations regarding similar phenomena will shed important understanding of these dynamic processes and perhaps even our understanding of potential early life scenarios.¹²¹

Combining PISA-supporting polymerization methods with compatible chemistries capable of leading to modifications of the vesicle membrane parameters, integrating additional time scales or spatially segregated or concomitant changes to physico-chemical state variables, provides a unique and robust scenario/tool combination where one can construct systems capable of increasing in complexity and functional capabilities. Therefore, we can extend the chemist's toolbox to generate new materials and system-based solutions which were previously unachievable.

Here we have presented our view of this extraordinary trans-disciplinary area of science and highlighted some of the progress in a selected set of problems associated with functionality, its design and implementation. We expect that when the design and implementation of function is complemented with fully adaptive chemistry, many more developments will be awaiting for us to make.

Conflicts of interest

There are no conflicts of interest to declare.

Acknowledgements

S. P. would like to thank Drs Chenyu Lin, Sai Krishna-Katla, Gong Cheng, Marta Dueñas-Díez and Thomas Draper for useful discussions regarding PISA and BZ chemistry. In addition to the above, J. P.-M. thanks former members of his group Drs Albertsen, Bastakoiti, Pereira de Souza, Ren and Szymanski for many enlightening discussions on PISA and on oscillatory chemistry and Drs Guo, Guragain, Poros-Tarcali and Srivastava for useful discussions on PISA. JP-M also thanks his colleagues in the Harvard Origins of Life Initiative, Profs. Stein Jacobsen, Andrew Knoll, Dimitar Sasselov and Jack Szostak and the students in the Origins of Life Consortium for many discussions. Discussions with Prof. C. Boyer, the late Prof. Murray Gell-Mann, Prof. Stephen Mann and Prof. Geoffrey West are gratefully acknowledged. This work was funded by Repsol, S. A. and we are very grateful for all their support. The funders had no role in study design, decision to publish, or preparation of the manuscript.

References

- 1 M. Lansalot and J. Rieger, *Macromol. Rapid Commun.*, 2019, **40**, 1800885.
- 2 J. Morris, D. Hartl, R. Lue, M. Michael, A. Knoll, A. Berry and A. Beiwener, *Biology: How Life Works*, W. H. Freeman, 3rd edn, 2019.
- 3 D. Boal, *Mechanics of the cell*, Cambridge University Press, 2nd edn, 2012.
- 4 D. Botstein, *Decoding the language of genetics*, Cold Spring Harbour Laboratory Press, 1st edn, 2015.
- 5 F. Crick, *Life Itself: Its Origin and Nature*, Simon and Schuster, 1st edn, 1981.
- 6 J. C. Gilbert and S. F. Martin, *Experimental Organic Chemistry: A Miniscale & Microscale Approach*, Cengage Learning, 6th edn, 2012.
- 7 F. Serratos, *Organic Chemistry in Action*, Elsevier Science, 1st edn, 1990.
- 8 G. Cheng and J. Pérez-Mercader, *Macromol. Rapid Commun.*, 2019, **40**, 1800513.
- 9 I. A. Chen and P. Walde, *Cold Spring Harbor Perspect. Biol.*, 2010, **2**, a002170.
- 10 J. Maynard Smith and S. Eörs Szathmáry, *The Major Transitions in Evolution*, Oxford University Press, Reprint edn, 1995.
- 11 G. Nicolis and I. Prigogine, *Self-organization in nonequilibrium systems: from dissipative structures to order through fluctuations*, Wiley, 1st edn, 1977.
- 12 G. Lebon, D. Jou and J. Casas-Vázquez, *Understanding non-equilibrium thermodynamics: Foundations, applications, frontiers*, Springer, 2008.
- 13 J. D. Halley and D. A. Winkler, *Complexity*, 2008, **14**, 10–17.
- 14 S. A. P. Van Rossum, M. Tena-Solsona, J. H. Van Esch, R. Eelkema and J. Boekhoven, *Chem. Soc. Rev.*, 2017, **46**, 5519.
- 15 A. J. Bissette and S. P. Fletcher, *Angew. Chem., Int. Ed.*, 2013, **52**, 12800–12826.
- 16 G. J. M. Koper, J. Boekhoven, W. E. Hendriksen, J. H. Van Esch, R. Eelkema, I. Pagonabarraga, J. M. Rubí and D. Bedeaux, *Int. J. Thermophys.*, 2013, **34**, 1229–1238.
- 17 M. B. Adelnik, B. A. Fisher, C. Larive, C.-J. Li, K. Matyjaszewski, A. A. Spector, M. A. White and G. Wnek, *McGraw-Hill Concise Encyclopedia of Chemistry*, McGraw-Hill, 1st edn, 2004.
- 18 R. P. Feynman, *The Feynman Lectures on Physics, Vol. I: The New Millennium Edition: Mainly Mechanics, Radiation and Heat*, Basic Books, Millen edn, 1963.
- 19 R. C. Desai and R. Kapral, *Dynamics of Self-Organized and Self-Assembled Structures*, Cambridge University Press, 1st edn, 2009.
- 20 P. M. Chaikin and T. C. Lubensky, *Principles of condensed matter physics*, Cambridge University Press, 7th edn, 2013.
- 21 J. Israelachvili, *Colloids Surf., A*, 1994, **91**, 1–8.



- 22 J. Israelachvili, *Intermolecular and Surface Forces*, Academic Press, 3rd edn, 2011.
- 23 J. Rieger, *Macromol. Rapid Commun.*, 2015, **36**, 1458–1471.
- 24 Y. Mai and A. Eisenberg, *Chem. Soc. Rev.*, 2012, **41**, 5969–5985.
- 25 M. Dueñas-Díez and J. Pérez-Mercader, *iScience*, 2019, **19**, 514–526.
- 26 B. P. Bastakoti and J. Perez-Mercader, *Angew. Chem., Int. Ed.*, 2017, **56**, 12086–12091.
- 27 B. P. Bastakoti and J. Perez-Mercader, *Adv. Mater.*, 2017, **29**, 1704368.
- 28 R. Srivastava, M. Dueñas-Díez and J. Pérez-Mercader, *React. Chem. Eng.*, 2018, **3**, 216–226.
- 29 L. Hou, M. Dueñas-Díez, R. Srivastava and J. Pérez-Mercader, *Commun. Chem.*, 2019, **2**, 1.
- 30 B. M. Discher, Y. Y. Won, D. S. Ege, J. C. M. Lee, F. S. Bates, D. E. Discher and D. A. Hammer, *Science*, 1999, **284**, 1143–1146.
- 31 L. Jin, A. E. Engelhart, K. P. Adamala and J. W. Szostak, *J. Visualized Exp.*, 2018, **132**, e57324.
- 32 U. Seifert, K. Berndt and R. Lipowsky, *Phys. Rev. A*, 1991, **44**, 1182–1202.
- 33 S. Sugihara, A. Blanz, S. P. Armes, A. J. Ryan and A. L. Lewis, *J. Am. Chem. Soc.*, 2011, **133**, 15707–15713.
- 34 T. F. Zhu, K. Adamala, N. Zhang and J. W. Szostak, *Proc. Natl. Acad. Sci. U. S. A.*, 2012, **109**, 9828–9832.
- 35 A. I. Oparin, *The Origin of Life*, Macmillan, New York, 3rd edn, 1938.
- 36 T. Y. Dora Tang, C. Rohaida Che Hak, A. J. Thompson, M. K. Kuimova, D. S. Williams, A. W. Perriman and S. Mann, *Nat. Chem.*, 2014, **6**, 527–533.
- 37 S. Koga, D. S. Williams, A. W. Perriman and S. Mann, *Nat. Chem.*, 2011, **3**, 720–724.
- 38 M. M. K. Hansen, L. H. H. Meijer, E. Spruijt, R. J. M. Maas, M. V. Rosquelles, J. Groen, H. A. Heus and W. T. S. Huck, *Nat. Nanotechnol.*, 2016, **11**, 191–197.
- 39 “boot v4.”, *O. E. D. Online*, June 2020.
- 40 A. N. Albertsen, J. K. Szymański and J. Pérez-Mercader, *Sci. Rep.*, 2017, **7**, 41534.
- 41 G. Cheng and J. Perez-Mercader, *Chem.*, 2020, **6**, 1160–1171.
- 42 S. Jain and F. S. Bates, *Macromolecules*, 2004, **37**, 1511–1523.
- 43 R. C. Hayward and D. J. Pochan, *Macromolecules*, 2010, **43**, 3577–3584.
- 44 N. S. Cameron, M. K. Corbierre and A. Eisenberg, *Can. J. Chem.*, 1999, **77**, 1311–1326.
- 45 L. Zhang and A. Eisenberg, *Science*, 1995, **268**, 1728–1731.
- 46 L. Zhang, K. Yu and A. Eisenberg, *Science*, 1996, **272**, 1777–1779.
- 47 M. J. Derry, L. A. Fielding and S. P. Armes, *Prog. Polym. Sci.*, 2016, **52**, 1–18.
- 48 W. M. Wan, X. L. Sun and C. Y. Pan, *Macromol. Rapid Commun.*, 2010, **31**, 399–404.
- 49 S. L. Canning, G. N. Smith and S. P. Armes, *Macromolecules*, 2016, **49**, 1985–2001.
- 50 F. D'Agosto, J. Rieger and M. Lansalot, *Angew. Chem.*, 2020, **59**, 8368–8392.
- 51 A. Blanz, J. Madsen, G. Battaglia, A. J. Ryan and S. P. Armes, *J. Am. Chem. Soc.*, 2011, **133**, 16581–16587.
- 52 F. Huo, S. Li, X. He, S. A. Shah, Q. Li and W. Zhang, *Macromolecules*, 2014, **47**, 8262–8269.
- 53 A. Blanz, A. J. Ryan and S. P. Armes, *Macromolecules*, 2012, **45**, 5099–5107.
- 54 J. C. Foster, S. Varlas, B. Couturaud, J. R. Jones, R. Keogh, R. T. Mathers and R. K. O'Reilly, *Angew. Chem., Int. Ed.*, 2018, **57**, 15733–15737.
- 55 Y. Zhang, L. Yu, X. Dai, L. Zhang and J. Tan, *ACS Macro Lett.*, 2019, **8**, 1102–1109.
- 56 S. J. Byard, C. T. O'Brien, M. J. Derry, M. Williams, O. O. Mykhaylyk, A. Blanz and S. P. Armes, *Chem. Sci.*, 2020, **11**, 396–402.
- 57 Q. Ye, M. Huo, M. Zeng, L. Liu, L. Peng, X. Wang and J. Yuan, *Macromolecules*, 2018, **51**, 3308–3314.
- 58 N. J. Warren, O. O. Mykhaylyk, A. J. Ryan, M. Williams, T. Doussineau, P. Dugourd, R. Antoine, G. Portale and S. P. Armes, *J. Am. Chem. Soc.*, 2015, **137**, 1929–1937.
- 59 C. Gonzato, M. Semsarilar, E. R. Jones, F. Li, G. J. P. Krooshof, P. Wyman, O. O. Mykhaylyk, R. Tuinier and S. P. Armes, *J. Am. Chem. Soc.*, 2014, **136**, 11100–11106.
- 60 J. Lesagedelachaye, X. Zhang, I. Chaduc, F. Brunel, M. Lansalot and F. D'Agosto, *Angew. Chem., Int. Ed.*, 2016, **55**, 3739–3743.
- 61 M. Huo, Z. Xu, M. Zeng, P. Chen, L. Liu, L. T. Yan, Y. Wei and J. Yuan, *Macromolecules*, 2017, **50**, 9750–9759.
- 62 H. G. Döbereiner, *Curr. Opin. Colloid Interface Sci.*, 2000, **5**, 256–263.
- 63 D. E. Discher and A. Eisenberg, *Science*, 2002, **297**, 967–973.
- 64 Y. Hu and J. Pérez-Mercader, *Colloids Surf., B*, 2016, **146**, 406–414.
- 65 E. Yoshida, *Colloid Polym. Sci.*, 2013, **291**, 2733–2739.
- 66 E. Yoshida, *Colloid Polym. Sci.*, 2014, **292**, 1463–1468.
- 67 J. K. Szymanski and J. Perez-Mercader, *Polym. Chem.*, 2016, **7**, 7211–7215.
- 68 K. Ren and J. Perez-Mercader, *Polym. Chem.*, 2018, **9**, 3594–3599.
- 69 J. Guo, E. Poros-Tarcali and J. Perez-Mercader, *Chem. Commun.*, 2019, **55**, 9383–9386.
- 70 S. Perrier, *Macromolecules*, 2017, **50**, 7433–7447.
- 71 N. J. W. Penfold, J. Yeow, C. Boyer and S. P. Armes, *ACS Macro Lett.*, 2019, **8**, 1029–1054.
- 72 J. Tan, H. Sun, M. Yu, B. S. Sumerlin and L. Zhang, *ACS Macro Lett.*, 2015, **4**, 1249–1253.
- 73 Y. Zhang, J. He, X. Dai, L. Yu, J. Tan and L. Zhang, *Polym. Chem.*, 2019, **10**, 3902–3911.
- 74 L. D. Blackman, K. E. B. Doncom, M. I. Gibson and R. K. O'Reilly, *Polym. Chem.*, 2017, **8**, 2860–2871.
- 75 J. Yeow, O. R. Sugita and C. Boyer, *ACS Macro Lett.*, 2016, **5**, 558–564.
- 76 J. Tan, Q. Xu, X. Li, J. He, Y. Zhang, X. Dai, L. Yu, R. Zeng and L. Zhang, *Macromol. Rapid Commun.*, 2018, **39**, 1700871.



