
# Volume 3 Number 9 7 May 2022 Pages 3665-4040

# Materials Advances



ISSN 2633-5409

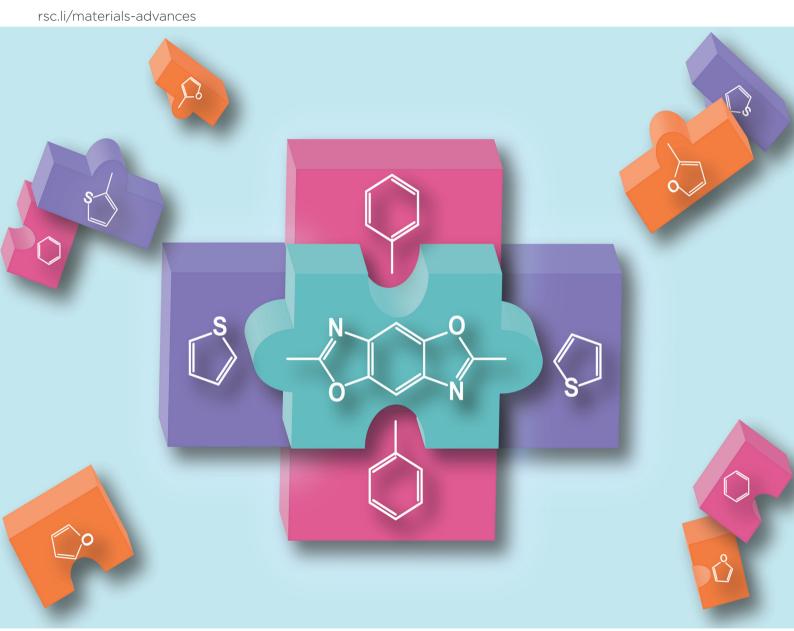

#### PAPER

# **Materials Advances**



View Article Online PAPER



Cite this: Mater. Adv., 2022, **3**, 3842

Received 25th October 2021, Accepted 5th February 2022

DOI: 10.1039/d1ma00990g

rsc.li/materials-advances

## A computational and experimental investigation of deep-blue light-emitting tetraarylbenzobis[1,2-d:4,5-d']oxazoles†

In an effort to design deep-blue light emitting materials for use in OLEDs, the optical and electronic properties of a series of tetraarylbenzobis[1,2-d:4,5-d']oxazole (BBO) cruciforms were evaluated using density functional theory (DFT) and time-dependent DFT (TD-DFT). Of the nine possible combinations of phenyl-, furan-2-yl-, and thiophen-2-yl-substituted BBO cruciforms, five were predicted to have ideal optical and electronic properties for use in blue-light emitting diodes. These five cruciforms were synthesized and then characterized electrochemically and spectroscopically. Additionally, they were solution-processed into functional organic light-emitting diodes (OLED). Several of the OLEDs exhibited deep-blue EL ( $\lambda_{EL}$  < 452 nm; CIE $_{V}$   $\leq$  0.12) with maximum luminance efficacies reaching 0.39 lm W<sup>-1</sup> and maximum current efficiencies of 0.59 cd A<sup>-1</sup>. A comparison of identical device architectures showed that heterocycles such as furan and thiophene helped improve device efficiencies with only a minor red-shift of the electroluminescence (EL). Although these BBO cruciforms produced the desired deep-blue emission their modest performance in host-guest OLEDs demonstrates the incorporation of heterocycles onto the BBO cruciform motif is detrimental to the fluroescence quantum yield. These results add to the knowledge base on structure-property relationships that will inform the design of better blue emitting materials.

## Introduction

In the past four decades, the escalation of organic semiconductor (OSC) research has led to the discovery of numerous materials with properties suitable for use in applications such as photovoltaics, 1-4 electrochromics, 5-8 and organic lightemitting diodes (OLED)s.9-11 As a result, these OSCs can be used to replace the expensive, sometimes toxic, inorganic materials currently used in modern technology. The semiconducting properties of OSC is a result of the extensive delocalization of the  $\pi$ -electrons within these materials. One positive aspect of OSC is that the opto-electronic properties can be fine-tuned via structural modification for specific applications. As a result, understanding the relationship

between and OSCs structure and it's properties is imperative

advent of new display and lighting applications. OLEDs have several advantages over conventional inorganic LEDs. For example, OLED displays can be fabricated via solution-processing techniques like inkjet printing, eliminating the need for thermal evaporation of various layers. This enables the facile production of large area devices with lower fabrication costs.12 OLEDs can convert up to 100% of injected charges into photons, maximizing light output while minimizing the amount of energy wasted as thermal radiation. 13 Furthermore, unlike inorganic LEDs, OLEDs do not require the use of backlighting and thus can achieve the high contrast ratio that is considered in the industry as "true-black". 14 As a result of these advantages, OLEDs are currently being used in cell phones and displays.<sup>13</sup>

While OLEDs have a bright future for use in consumer applications, their operational lifetimes impede the wide-spread commercial-utility of this technology. It is common for blueemissive materials to degrade an order of magnitude faster than both the red and green emissive materials. 15 This is due to several factors including the greater amount of heat generated by blue-fluorescent OLEDs and the high S<sub>1</sub> energy level of the blue fluorescent materials ( $\sim$  3.0 eV). This is higher than the C-P bond

for developing a useful material. Recently, there has been renewed interest in OLEDs due to the

<sup>&</sup>lt;sup>a</sup> Department of Chemistry, Boston University, Boston, MA 02215, USA. E-mail: malikaj@bu.edu

<sup>&</sup>lt;sup>b</sup> Department of Chemistry and Biochemistry, University of North Georgia, Dahlonega, GA 30041, USA

<sup>&</sup>lt;sup>c</sup> Division of Materials Science and Engineering, Boston University, Boston, MA 02215. USA

<sup>†</sup> Electronic supplementary information (ESI) available: <sup>1</sup>H and <sup>13</sup>C NMR spectra, Photoluminescent spectra, AFM images, cyclic voltammograms. See DOI: 10.1039/d1ma00990g

**Materials Advances Paper** 

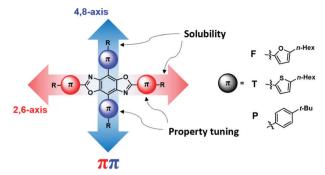


Fig. 1 General structure of benzobis[1,2-d:4,5-d']oxazole cruciforms with aryl substituents used in the study

energy and equal to the energy of the C-N bond favoring bond homolysis. 15,16 As most display and lighting technologies rely on a combination of different colors to produce a gamut of detectable chromaticities, the degradation of one component renders the device unusable. While there have been some recent breakthroughs, such as the development of hyperfluorescent OLEDs, 17,18 the development of electrochemically stable deepblue OLEDs remains challenge.

Our group has focused on the development of novel organic semiconductors based on benzobis[1,2-d;4,5-d']oxazole (BBOs) cruciforms and their application in organic electronics. 19-22 These materials are comprised of four aryl-substituents along the central benzene ring (4,8-(2,6-position/axis)), Fig. 1.<sup>23,24</sup> This arrangement creates spatially segregated frontier molecular orbitals (FMOs), facilitating the nearly independent tuning of the HOMO and LUMO levels, respectively using aromatic substitution. 24-26 Using steric hindrance, the HOMO and LUMO energies can be further altered for better alignment between various charge-transport layers without altering the optical band gap  $(E_{gr}^{opt})^{21}$ . These substituents can be further functionalized with alkyl-chains to increase their solubility for solutionprocessing capabilities. Materials based on this heterocycle are also known to have high thermal decomposition temperatures and excellent oxidative stability. 27-30 While the tunable nature of cruciforms makes them exciting candidates for use in a myriad of technologies, <sup>24–26</sup> the BBO moiety shows great promise for use in OLED application. 31-36 Previously, we reported a series of BBO cruciforms bearing phenyl- and fluoren-2-yl-substituents, which displayed deep-blue emission with maximum luminance efficiencies as high as ~2 cd A<sup>-1</sup> and Commission Internationale de L'Eclairage (CIE) coordinates of (0.15  $\leq x \leq$  0.17, 0.05  $\leq y \leq$  $0.11).^{32}$ 

To improve upon the cruciform design motif, we have designed a series of nine BBO cruciforms bearing all possible pairings using phenyl-, furan-2-yl-, or thiophene-2-yl-substituents at the two axes. Benzenoid compounds have been shown to produce wide-band gap materials. OSCs incorporating the heterocycle furan have been shown to be highly fluorescent materials.<sup>37–39</sup> Whereas, thiophene-containing materials are known to exhibit high electrochemical stabilities and good charge-transport properties for a variety of electronic technologies. 40,41 While benzene and thiophene-containing BBOs have been synthesized, these materials have not been investigated in active OLED devices. Herein, we report the theoretical and experimental findings of a series of BBO cruciforms and their performance in solution-processed OLEDs.

## Results and discussion

## Computational predictions

To identify the most promising candidates (those with  $E_{\rm g}^{\rm opt}$  greater than 2.80 eV), density functional theory (DFT) and timedependent DFT (TD-DFT) computations were performed at the mPW3PBE/SV level.21 All simulated spectra can be found in the supplemental information section along with detailed excited state analyses. The calculated electronic energy levels, FMOs assigned with percentage of electron location, and ground state dihedral angles are collated in Table 1. A discussion of calculated LUMO energies is not included due to the variability in theoretical modelling of electron affinity.21

The structure-property study began with an examination of the HOMO level. The two lowest HOMO levels were PP and TP both of which were the only two which possessed non-planar structures with an out-of-plane contortion along the 4,8-axis of 26.2° and 23.0°, respectively. The lack of planarity in these two cruciforms produced levels that were  $\geq 0.09$  eV lower than the third lowest lying HOMO exhibited by FP. Overall, placement of the phenyl ring along the 4,8-axis produced the lowest levels likely due to the strong aromaticity of the benzene. Additionally, substitutions along the 4,8-axis produced HOMO levels differences of 0.37 eV (PP, PF, PT), 0.28 eV (FP, FF, FT) and 0.35 eV (TP, TF, TT) thereby suggesting that the HOMO level may be tuned utilizing this axis. Irrespective of the aryl group identity at the 4,8-axis, the HOMO level was most stabilized by a phenyl ring followed by thiophenyl and finally furanyl with differences ranging from 0.03 to 0.12 eV which indicates that changes along the 2,6-axis do not significantly impact the HOMO level. Finally, in all cases the electron density for the HOMO was localized along the 4,8-axis with PF and PP demonstrating the largest percentage of localization at 95.8% (Fig. 2).

Compounds bearing thiophene at the 4,8-positions have an average HOMO of -5.63 eV while those with furan are slightly increased to approximately -5.55 eV. Since all cruciforms without benzene rings at the 4,8-axis are predicted to be

Table 1 Theoretical electronic energies, electron density localization and geometric predictions of the investigated BBOs in the ground-state

			Loca	lizatio	n (%)			
	Energy Lev	НОМО		LUMO		Dihedral Angles (°)		
ВВО	НОМО	$E_{ m g}^{ m opt}$	4,8	2,6	4,8	2,6	4,8	2,6
PP	-5.94	3.17	84.4	15.6	28.8	71.2	153.8	176.9
PF	-5.57	2.83	95.8	4.2	39.1	60.9	180.0	180.0
PT	-5.64	2.79	95.8	4.2	48.8	51.2	180.0	180.0
FP	-5.82	2.96	81.4	18.6	28.4	71.6	180.0	180.0
FF	-5.53	2.78	92.0	8.0	29.7	70.3	180.0	180.0
FT	-5.61	2.74	92.9	7.1	44.8	55.2	180.0	180.0
TP	-5.91	2.97	73.8	26.2	18.1	81.9	157.0	178.2
TF	-5.56	2.66	91.6	8.4	20.5	79.5	180.0	180.0
TT	-5.64	2.63	92.5	7.5	32.1	67.9	180.0	180.0

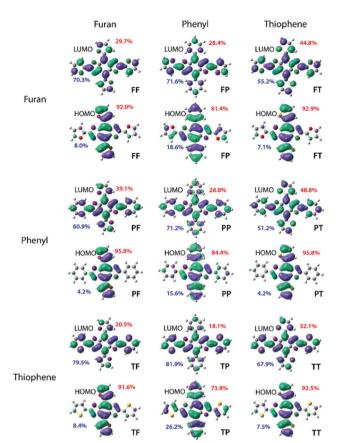


Fig. 2 FMOs of the nine computationally studied systems. Compound names are listed bottom right of each structure. Percentages in red correspond to the total electron density that lies along the 4,8-axis while that in blue quantifies the 2,6-axis.

completely planar, this indicates the energy differences are solely due to aryl-substituent identity. Thus, the slight increase in energy for cruciforms with furan at the 4,8-axis is most likely due to the decreased aromaticity of the furan unit.

Based on the calculated band gap  $(E_g^{\text{opt}})$  there were several promising deep-blue emissive candidates. Of the nine cruciforms, those bearing benzene rings produced the largest  $E_g^{\text{opt}}$ . Three cruciforms (PP, TP, and FP) had band gaps ranging from 2.96-3.17 eV. Moreover, the simulated UV-Vis spectra for these compounds all show very little tailing in the visible spectrum, further supporting their classification as potential deep-blue emitters. Two other compounds, PT and PF, were found to exhibit  $E_{\rm g}^{\rm opt}$  values close to the lower limit of blue-emitters (2.79–2.83 eV) with minor absorption in the visible spectrum. Although their structural isomers show more promise as deep-blue dopants, these BBOs were also included in the study to investigate structure-property relationships. The other cruciforms had smaller  $E_{\rm g}^{\rm opt}$  (2.78–2.63 eV), thereby red-shifting the absorbance profiles. Thus, TT, TF, TF, and FF were omitted as synthetic targets.

## **Synthesis**


The synthetic pathways for the functional arenes are shown in the ESI.† All five BBOs were synthesized using a tandem

approach: a condensation reaction to introduce aryl substituents along the 2,6-axis followed by a cross-coupling reaction to attach substituents at the 4,8-axis. The formation of the final BBOs is outlined in Scheme 1. First, 2,5-diamino-3,6-dibromo-*p*-hydroquinone was condensed with either the benzoic acid to form 26P48Br or orthoesters to form 26F48Br, and 26T48Br. The benzene substituent was coupled along 4,8-axis using traditional Suzuki–Miyaura cross-coupling conditions, providing compounds FP, TP, and PP in good yields. The furan and thiophene units were attached to the 4,8-positions using Stille cross-coupling techniques, yielding PF and PT in good yields. Upon purification, all compounds were found to be moderately soluble in chloroform and characterized by <sup>1</sup>H and <sup>13</sup>C NMR spectroscopy, HR-MS (ESI), thermogravimetric analysis (TGA), and melting point determination.

## Electronic and optical properties

The experimental electronic and optical properties of all synthesized compounds were investigated using cyclic voltammetry, UV-Vis spectroscopy, and photoluminescence spectroscopy in solution and thin film. All pertinent data can be found in Table 2. The electrochemical oxidation potentials (Fig. S25-S29, ESI†) were used to calculate the HOMO energy while the LUMO level was found by adding the onset of absorbance to the HOMO level. The HOMO levels of each material range from -5.74 to -5.25 eV while the LUMO energies range from -2.68 to -2.52 eV. It was observed that when the phenyl substituents are placed through the 4,8-axis, the HOMO energy was lowered when compared to the placement of electron-rich substituents, such as furan and thiophene. Moreover, the solution-state voltammograms indicate good stability of most BBOs as seen by the reproducibility of three consecutive redox cycles. However, PF a exhibits slight change with each sequential redox cycle, indicating this material exhibits the highest level of instability of the set.

The experimental UV-Vis results show very good correlation to the theoretical model, see ESI.† Due to the limited solubility of these compounds, all five BBOs were able to be dissolved in either toluene or chloroform as 0.01 gL<sup>-1</sup> equimolar solutions. The peak maxima for each BBO show very little difference (<6 nm) between the two solvent media (see ESI†), suggesting that all 5 BBOs exhibit more locally excited (LE) character between the ground and excited states. In chloroform, there is a distinct pattern between aryl-substitution and absorbance profiles, Fig. 3. The spectrum for **PP** exhibits a peak maximum centred at 354 nm with small spectral features contributing to the peak breadth ( $\sim$ 345 nm and 376 nm) When the 2,6-axis substituent is changed to either furan or thiophene, the absorbance profile undergoes a bathochromic shift of 17 nm and 28 nm for FP and TP, respectively. For both compounds, the low energy transitions occur between ~325 to ~415 nm which is ideal for deep-blue OLED dopants. As thin films, the peak maximum for FP is red-shifted by 9 nm while **TP** is shifted by 8 nm due to  $\pi$ - $\pi$ stacking interactions. When the aryl substituents along the 4,8axis of PP are switched to furan or thiophene (PF and PT), the absorbance profiles experience a bathochromic shift. Cruciform PF is shifted by 23 nm while PT shifts by 28 nm due to the

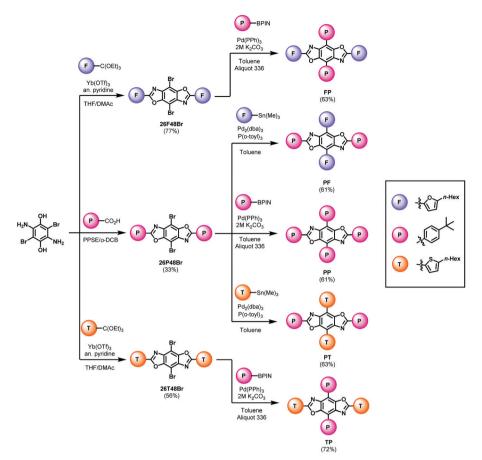

Scheme 1 Synthesis of the final BBO cruciform

Electronic and spectral properties of the five BBOs

Electronic		Optio	al								
			Solut	ion State			Solid State				
ВВО	HOMO <sup>a</sup> (eV)	LUMO <sup>b</sup> (eV)		$ \begin{array}{l} \varepsilon^d \left(10^4\right) \\ \left(M^{-1} \text{ cm}^{-1}\right) \end{array} $	$\lambda_{\max}^{abs} {}^{e} [CF] (nm)$	$\lambda_{\max}^{\text{em}} \left[ \text{CF} \right] $ (nm)	$\lambda_{\max}^{em}{}^e$ [Tol] (nm)	Lifetime <sup>f</sup> (ns)	$\Phi^g$ (%)	$\lambda_{\max}^{abs} (nm)$	$\lambda_{\max}^{\text{em}}{}^{e}$ $(\text{nm})^{\text{e}}$
PP	-5.74	-2.60	3.14	7.0	291, 354	<b>422</b> , 406	<b>427</b> , 408	1.96	44	299, 362	445
PF	-5.25	-2.52	2.73	5.1	<b>371</b> , 355, 321, 303	478*, <b>453</b>	494, 472	1.94	22	<b>388</b> , 300	546
PT	-5.28	-2.55	2.73	5.4	407, 377, 359, 330, 318	479, <b>451</b>	472, <b>445</b>	2.20	26	418, 380, 365, 334, 277	569*, <b>544</b>
FP	-5.65	-2.59	3.06	6.4	390, <b>371</b> , 356	440, 413	459*, <b>430</b> , 410	1.38	60	402, <b>380</b> , 364, 301	<b>489</b> , 461*
TP	-5.65	-2.68	2.97	6.2	402, 382, 365, 306	456, <b>432</b>	471*, <b>444</b> , 421	NA	45	414, <b>390</b> , 372, 309, 266	458

<sup>&</sup>lt;sup>a</sup> HOMO values were determined from onset of oxidation using cyclic voltammetry and compared to a ferrocene standard. <sup>b</sup> LUMO = HOMO + E<sub>g</sub><sup>opt</sup>. <sup>c</sup> Optical band gaps determined from onset of absorbance in solution. <sup>d</sup> Experimental absorption coefficients were calculated from peak maxima at concentrations of 0.01 g L<sup>-1</sup>, 0.005 g L<sup>-1</sup>, and 0.0017 g L<sup>-1</sup>. <sup>e</sup> Bold values indicate peak of maximum absorbance/emission. Values with \* following indicate spectral shoulders. f Acquired in chloroform. Found in chloroform.

chalcogens. Both BBOs also exhibit a broad series of low-energy transitions at  $\sim$ 385 to  $\sim$ 460 nm demonstrating that even dispersed in solution, these compounds start to absorb in the visible spectrum. Moreover, when compounds PF and PT are cast as thin films, the absorbance profile becomes quite broad, thus losing the resolution between observable transitions.

The photoluminescence (PL) spectra were measured in CHCl<sub>3</sub> to determine emission profiles and quantum yields for each BBO (Fig. 3; Table 2). Since a host-guest active layer is

used in the OLED devices for this study, the neat film data, available in the ESI,† will not be discussed. In solution, PP exhibited two emission peaks at 406 and 422 nm with a quantum yield of 44%. Switching the 2,6-substituent to furan (FP) provides a slight hypsochromic shift in emission by 8 nm whereas the thiophene substituent (TP) bathochromically shifts the PL spectra by 10 nm. Interestingly, the substitution of furan increases the quantum yield of the compound to 60% while the use of thiophene kept the quantum yield relatively constant

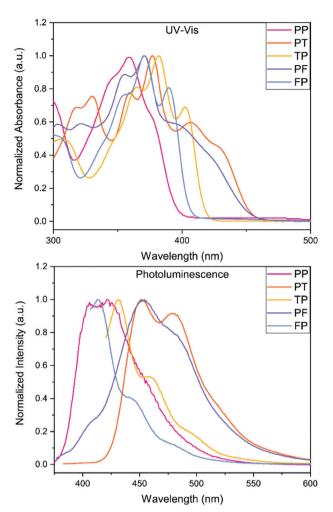


Fig. 3 UV-Vis spectra (top) and photoluminescence (bottom) of the five BBOs in chloroform (0.01  $\text{q L}^{-1}$ ).

(45%) when compared to **PP** (44%). **FP**, **TP** and **PP** are in a suitable range of emission for deep-blue OLEDs. As hypothesized, changes to the 4,8-aryl substituent (**PF** and **PT**) produced more cyan emission where the furan variant exhibits a PL maximum red-shift of 31 nm while the thiophene counterpart shows a comparable shift of 29 nm. Moreover, this conjugation pattern considerably lowers the PL quantum yields (22–26%) compared to that of **PP**.

We next investigated the radiative lifetimes of the five BBOs to assess their photoluminescent behaviour. Excluding TP which was unable to be measured, the BBOs emit light under 2.30 ns, further supporting the hypothesized LE character of the materials and suggesting traditional fluorophore behaviour as OLED emitters. While **PF** and **PT** are believed to be less than ideal as deep-blue dopants, these materials were used in OLED devices to elucidate the structure–property trends when compared to their counterparts **FP** and **TP**.

## **OLED** device properties

The device characteristics of each BBO were evaluated as dopants in a mixed-host matrix. The host-guest architecture

has proven to be a beneficial motif for small molecule-based OLEDs. The mixed host strategy was employed to reduce the energetic barrier from PEDOT:PSS to the active layer by integrating in common hole transport layer (HTL) material, 4,4′,4″-tris(*N*-carbazolyl)triphenylamine (TCTA). By blending this material into the active layer, better positive charge injection into the A electrode occurs and is met with better recombination. <sup>42,43</sup> The device configuration for all studies was as follows: ITO (100 nm)/PEDOT:PSS (35 nm)/5% BBO, 1:1 26DCzPPY:TCTA/TmPyPB (35 nm)/LiF (1 nm)/Al (100 nm). The electroluminescence (EL) spectra, external quantum efficiencies (EQE), and energy level diagram for all compounds used are illustrated in Fig. 4. Photoluminescence spectra of the active layers are displayed in the ESI† (Fig. S26, ESI†)

Each cruciform exhibited EL that closely matched their solid-state PL spectra corresponding to the same active layer composition. Compounds **PF** and **PT** exhibited the most redshifted EL with peak maxima at 487 nm and 476 nm, respectively, producing sea-green emission. The EL for the for isomers hypsochromically shifted to 442 and 451 for **FP** and **TP**, respectively. Resulting from the large  $E_{\rm g}^{\rm opt}$ , cruciform **PP** had the bluest EL with a peak maxima of 434 nm. Of the five BBOs, compounds **FP**, **TP** and **PP** all exhibited CIE<sub>x</sub> components around 0.15 and CIE<sub>y</sub> components < 0.12, making them ideal candidates for deep-blue dopants.  $^{44-50}$ 

We next examined the device parameters to determine the performance of each BBO. The device efficiencies/outputs are shown in Table 3. All compounds exhibited low turn-on voltages (measured at 1 cd m<sup>-2</sup>), ranging between 3.3-4.0 V, while driving voltages (100 cd  $\text{m}^{-2}$ ) were found between 4.4–5.1 V. We attribute the low driving voltages to the mixed-host system and donor/ acceptor units of each BBO, allowing good injection of positive and negative charges into the active layer. The maximum achievable luminance  $(L_{max})$  for **PP** and **FP** were comparable at  $\sim$  530 cd m<sup>-2</sup> whereas **TP** had more than twice the luminance (1288 cd m<sup>-2</sup>). While blue emission was not obtained for PF and PT, compounds with thiophene substituents did significantly enhance each OLED's  $L_{\text{max}}$ . The placement of aryl substituents also provides a moderate luminance enhancement. For example, compared to **TP**, the isomer **PT** had a  $L_{\text{max}}$  value of 1572 cd m<sup>-2</sup>. The same effect is noted between the isomers FP and PF. All five compounds produce luminance levels suitable for display technology but do exhibit complications with regards to stability. Compounds PP, PT and PF all show irreversible device degradation after surpassing the potential corresponding to  $L_{\text{max}}$ . However, by exchanging the location of aryl substituents, compounds TP and FP show an overall enhanced stability. These results are interesting as they could indicate an important structure-property trend: the 4,8-axis controls the brightness of the device while the 2,6-axis extends the stability.

The device efficiencies for all BBO dopants showed results comparable to other small molecule, BBO-based OLEDs.<sup>32</sup> Compound **PP** was found to exhibit the lowest current efficiency (CE) and luminous efficacy (LE) of all emissive BBOs with an overall EQE of 0.37%. Our previous hypothesis stated this compound exhibited poor device performance in part due

Paper

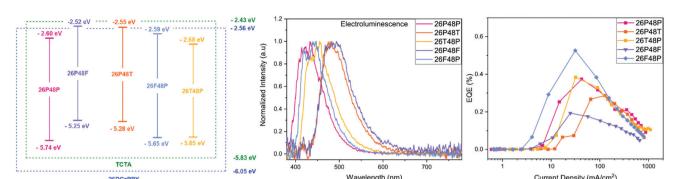


Fig. 4 (Left) Band diagram of five BBO dopants in mixed-host matrix. (Middle) Electroluminescence of BBO-based devices. (Right) EQE vs. Current Density map of the five devices

Table 3 Device properties of the BBO-based OLEDs. Bold values indicate maximum emission peak.  $V_{\rm on}$  = voltage at 1 cd m<sup>-2</sup>.  $V_{\rm 100}$  = driving voltage at 100 cd m<sup>-2</sup>.  $CE_{100}$  = current efficiency at 100 cd m<sup>-2</sup>.  $PE_{100}$  = luminous efficacy at 100 cd m<sup>-2</sup>

вво	$\lambda^{EL}$ (nm)	CIE $(x, y)$	$V_{\rm on}$ (V)	V <sub>100</sub> (V)	$L_{\rm max}~({\rm cd}~{\rm m}^{-2})$	CE <sub>100</sub> (cd A <sup>-1</sup> )	$CE_{Max}$ (cd $A^{-1}$ )	PE <sub>100</sub> (lm W <sup>-1</sup> )	$PE_{Max} \left(lm \ W^{-1} \right)$	EQE <sub>Max</sub> (%)	RMS (nm)
PP	<b>434</b> , 419	0.16, 0.06	3.3	4.5	552.6	0.23	0.23	0.16	0.16	0.37	0.333
PT	476	0.17, 0.33	3.7	4.5	1572	0.32	0.59	0.22	0.35	0.29	0.322
TP	<b>451</b> , 433	0.15, 0.12	3.6	4.4	1288	0.33	0.40	0.24	0.28	0.38	0.394
PF	487	0.19, 0.36	4.0	5.1	784.4	0.32	0.36	0.20	0.21	0.21	0.339
FP	<b>442</b> , 420	0.15, 0.08	3.5	4.4	532.2	0.37	0.42	0.26	0.39	0.53	0.353
FP	<b>442</b> , 420	0.15, 0.08	3.5	4.4	532.2	0.37	0.42	0.26	0.39	0.53	0.353

to the planarity of the cruciform, causing luminescent quenching during device operation.5 However, comparing this data to observations for TP refutes this claim. Specifically, TP experiences nearly equivalent torsion about the 2,6- and 4,8-dihedral angles as PP and has higher CE and LE. Furthermore, compound FP, whose ground-state geometry is calculated to be completely planar experiences one of the highest CE/LE outputs with the highest EQE of 0.53%. Even reversing the axis, PF and PT all exhibit higher CE and LE values when compared to PP with EQEs of 0.21% and 0.29%, respectively. Therefore, we believe the reason PP can undergo EL in this study is due to the mixed-host system, while the poor efficiencies are due to the lack of aryl substituents which allow for more effective hole-transport to the dopant, such as thiophene and furan. However, the efficiencies of each device are overall poor and thus, it is evident that improvements must be made by altering fabrication conditions or utilizing new hosts.

To determine if the device performance was inhibited due to morphological constraints, each active layer was measured using atomic force microscopy (AFM). All AFM images are shown in Fig. S23 (ESI†) and roughness values are collated in Table 3. It is evident that the host-guest system employed using the mixed-host matrix provides excellent thin-films. The roughness for all active layers is <4 Å, suggesting that the morphological contributions towards poor device performance are negligible and that the issues could be due to factors at the molecular level. One possible explanation for the low CE/LE outputs could be due to the triplet state (T<sub>1</sub>) of each BBO cruciform. If a drastic energetic difference between the singlet  $(S_1)$  and  $T_1$  levels exists, this could result in the accumulation of charge-traps in the active layer. To assess this claim, preliminary DFT calculations show that the energy difference between the S<sub>1</sub> and T<sub>1</sub> states are between 0.941.09 eV (ESI†), supporting the hypothesis. Therefore, a more detailed degradation study of these materials is required to see what chemical or fabrication parameters can be altered to improve device performance and efficiencies.

## Conclusions

Guided by DFT predictions, we successfully identified a series of BBO cruciforms with deep-blue emissive character for OLEDs. The five candidates were synthesized in a few steps and solution-processed into functional devices for evaluation. The experimental opto-electronic properties closely matched DFT outputs and the results will be used to help improve the computational model for future predictions. Of the fivecandidates, compounds PP and FP all exhibited deep-blue emission (CIE<sub> $\nu$ </sub>  $\leq$  0.08) and luminance output useful for display technology. However, the lifetimes and efficiencies for the OLED devices were too low for practical usage. These experimental results indicate that we have the potential to control device stability and brightness through aryl-substitution at a specific BBO axis. The solution-processed active layer formed excellent thin-films, suggesting improvements should be made at the molecular level. Thus, our results affirms that BBO cruciforms are useful building blocks for the development of blue light-emitting materials, whose efficiencies can be enhanced through the inclusion of electron-rich heterocycles. Further studies into the photophysical properties and degradation analysis will improve the design of our BBOs, increasing the device efficiencies and lifetimes. With this information, potential of incorporating the structure of the deep-blue materials into

polymeric backbones could produce emissive polymers with mechanical properties suited for foldable technology.

## Experimental

## Computational methodology

All computations were performed using Gaussian 09 using the Comet supercomputer cluster provided by the San Diego Supercomputing Center through the Extreme Science and Engineering Discovery Environment (XSEDE). Compounds were then analysed through GaussView 6 GUI interface program package. Electronic ground state geometries were optimized using density functional theory (DFT) employing a mPW3PBE functional and an SV basis set verified through a frequency calculation. The first 15 excited states were generated through time dependent density functional theory (TD-DFT) applied to the optimized ground state for each oligomer. The HOMO, LUMO, band gap, FMOs, and UV-Vis simulations were generated from these excited computations.

#### Materials and methods

4,8-Dibromo-2,6-diethylbenzobisoxazole,19 and 2,5-diaminohyroquinone bishydrochloride<sup>51</sup> were synthesized according to literature procedures. THF was dried using an Innovative Technologies solvent purification system. All other chemical reagents were purchased from commercial sources and used without further purification unless otherwise noted. All column chromatography described was performed using a Teledyne CombiFlash® Rf+ system with solvents as specified. Nuclear magnetic resonance (NMR) experiments were carried out in CDCl<sub>3</sub> at 500 MHz (<sup>1</sup>H) AND 125 MHz (<sup>13</sup>C). In all spectra, chemical shifts are given in  $\delta$  relative to residual protonated solvent peak, CHCl<sub>3</sub> (7.26 ppm, <sup>1</sup>H; 77.16 ppm, <sup>13</sup>C). Coupling constants are reported in hertz (Hz). High-resolution mass spectra were recorded on a double-focusing magnetic sector mass spectrometer using ESI. Melting Points were determined using a MelTemp II apparatus equipped with thermometer. The electrochemical properties of the BBOs were investigated by cyclic voltammetry (CV) using a platinum working electrode in dichloromethane (solution) and acetonitrile (film), with 0.1 M Bu<sub>4</sub>NPF<sub>6</sub> as the electrolyte and an Ag/Ag<sup>+</sup> reference electrode. The onsets were referenced to Fc/Fc<sup>+</sup>. All UV-Vis and fluorescence spectra were obtained using quartz cuvettes with a 10 mm path length in CHCl3 or as spin-casted thin-films on a quartz slide (filtered 5 mg mL<sup>-1</sup> solution in CHCl<sub>3</sub> spun at 1500 RPM). Active layer fluorescence spectra were obtained using quartz slides filtered from 10 mg mL<sup>-1</sup> solution in chlorobenzene spun at 2000 RPM. UV-vis spectra were collected on a Shimadzu UV-1800 UV spectrophotometer. Photoluminescence spectra and absolute solution fluorescence quantum yields were obtained using a Varian Cary Eclipse Fluorimeter. Quantum yields were obtained with a HORIBA spectrophotometer Nanolog FL3-2iHR equipped with a Quanta-phi integrating sphere, respectively. The chloroform solution timeresolved fluorescence data for all the samples were collected

at 298 K on a time-correlated single-photon counting Edinburgh LifeSpec II and analyzed with the F980 software. A NanoLED of 405 nm was used as excitation source.

## Synthesis of precursors

**2-Hexylfuran (F1).** This compound was prepared according to previous literature. <sup>52</sup> Product is a colorless oil (89%, 60 mmol scale). <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>)  $\delta$  7.31 (d, J = 1.9 Hz, 1H), 6.29 (dd, J = 1.9, 3.1 Hz, 1H), 5.99 (d, J = 3.1 Hz, 1H), 2.64 (t, J = 7.6 Hz, 2H), 1.66 (quintet, J = 7.5 Hz, 2H), 1.41–1.28 (m, 6H), 0.92 (t, J = 6.7 Hz, 3H).

**2-Hexylthiophene (T1).** This compound was prepared analogously to compound **F1.** After purification with a hexanes column, the oil was subjected to distillation (Kugelrohr; 103 °C) to give a colorless oil. (65%, 75 mmol scale) <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>)  $\delta$  7.13 (dd, J = 4.9, 1.4 Hz, 1H), 6.95 (dd, J = 4.9, 3.3 Hz, 1H), 6.81 (m, 1H), 2.86 (t, J = 7.7 Hz, 2H), 1.72 (quintet, J = 7.5 Hz, 2H), 1.46–1.30 (m, 6H), 0.94 (t, J = 5.9 Hz, 3H).

**5-Iodo-2-hexylfuran** (**F2**). This compound was prepared according to previous literature.<sup>37</sup> slightly yellow oil (62%, 40 mmol scale). <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>)  $\delta$  6.41 (d, J = 3.2 Hz, 1H), 5.92 (d, J = 3.2 Hz, 1H), 2.65 (t, J = 7.7 Hz, 2H), 1.62 (quintet, J = 7.4 Hz, 3H), 1.39–1.25 (m, 11H), 0.90 (t, J = 6.8 Hz, 6H).

**5-Iodo-2-hexylthiophene** (T2). This compound was prepared according to previous literature.<sup>53</sup> slightly yellow oil (83%, 50 mmol scale). <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>)  $\delta$  7.05 (d, J = 3.5 Hz, 1H), 6.49 (d, J = 3.5 Hz, 1H), 2.81 (t, J = 7.6 Hz, 2H), 1.65 (quintet, J = 7.5 Hz, 2H), 1.42–1.25 (m, 6H), 0.91 (t, J = 6.9 Hz, 3H).

**2-Hexyl-5-(trimethylstannyl)furan (F3).** This compound was prepared according to previous literature and used without further purification or identification.<sup>37</sup> Orange oil.

2-Hexyl-5-(trimethylstannyl)thiophene (T3). This compound was prepared analogously to compound F3 and used without further purification or identification. Orange oil.

2-Hexyl-5-(triethoxymethyl)furan (F4). To an oven dried, N2 filled round bottom flask equipped with stir bar was added 1.22 g (50 mmol) of magnesium turnings. The solid was purged with N<sub>2</sub> twice before the addition of a small iodine crystal. These solids were stirred at 50 °C for 1 hour. After cooling to room temperature, 50 mL of anhydrous diethyl ether was added via cannula along with 4.6 mL (50 mmol) of 2-chloropropane. This suspension was fitted with a condenser and stirred at 35 °C for 1 hour, or until minimum magnesium was noticed. Upon cooling to room temperature, 5.56 g (20 mmol) of F2 was added through the top of the condenser and the solution was refluxed for 20 hours to produce a cloudy yellow-grey suspension. After cooling to room temperature, 6.3 mL (30 mmol) of tetraethylorthocarbonate was added through the top of the condenser and solution was returned to reflux for an addition 20 hours. Suspension becomes a milky-orange color after the reflux period ends. This solution is poured into ice-cold, conc. aqueous NH<sub>4</sub>Cl and extracted with diethyl ether. The organic layer is separated and washed with distilled water once, dried over sodium sulfate, and concentrated. Distillation was

**Materials Advances** Paper

performed using a Kugelrohr at 85 °C to remove excess tetraethylorthocarbonate and other volatiles to produce an orange oil as the final product. This oil was used without further purification. (79%).  ${}^{1}$ H NMR (500 MHz, CDCl<sub>3</sub>)  $\delta$  6.39 (d, 1H), 5.89 (d, 1H), 3.41 (q, 6H), 2.58 (t, 2H), 1.59 (quintet, 2H), 1.32-1.22 (m, 6H), 1.14 (t, 9H), 0.84 (t, 3H).

2-Hexyl-5-(triethoxymethyl)thiophene (T4). This product was prepared analogously to compound F4 using compound T2 as aryl halide. Orange oil (85%, 20 mmol scale). <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>)  $\delta$  6.95 (d, J = 3.6 Hz, 1H), 6.61 (d, J = 3.6 Hz, 1H), 3.43 (q, J = 7.1 Hz, 6H), 2.74 (t, J = 7.1 Hz, 2H), 1.64 (quintet, J = 7.4 Hz, 2H), 1.36–1.25 (m, 6H), 1.17 (t, J =7.1 Hz, 9H), 0.86 (t, J = 6.9 Hz 3H).

2-(4-(tert-Butyl)phenyl)-4,4,5,5-tetramethyl-1,3,2-dioxaborolane (P1). To an oven-dried RBF was added 4-tert-butylbromobenzene (10 mmol) and anhydrous THF (~30 mL). The solution was brought to -78 °C for the dropwise addition of *n*-butyllithium (1.3 mol eq.). The anion stirred for 45-60 minutes at -78 °C before addition of iPr-BPIN (1.5 mol eq). Upon addition, the solution was stirred overnight, slowly approaching room temperature. The solution was quenched with water and extracted with ethyl acetate. The organic layer was separated, washed twice with distilled water, and dried over Na2SO4. Concentration of crude product yielded a viscous oil which was purified using column chromatography (hexanes). Product is a crystalline, white, low-melting solid. (94%) <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>)  $\delta$  7.79 (d, J = 8.3 Hz, 2H), 7.43 (d, J = 8.3 Hz, 2H), 1.35 (s, 12H), 1.35 (s, 9H).

4-(tert-Butyl)benzoic acid (P2). An oven-dried round bottom flask equipped with stir bar and 35 mmol of magnesium turnings was cooled under vacuum and purged with N<sub>2</sub> three times. A catalytic amount of iodine was added to the flask and the turnings were stirred for 1 hour at 50 °C for activation. The flask was cooled to room temperature before the addition of anhydrous THF (100 mL). Next, 30 mmol of 4-tertbutylbromobenzene was added dropwise to the flask and allowed to stir for two hours. Afterwards, the solution was brought to -78 °C and was bubbled with CO<sub>2</sub>. Once bubbling started, the solution was removed from the dry-ice/acetone bath and allowed to return to room temperature ( $\sim 1$  hour). Upon completion, the solution was poured into 6 M HCl for 2 hours of stirring. The precipitate which formed was dissolved in DCM, separated from the aqueous layer, washed with water twice, and dried over Na<sub>2</sub>SO<sub>4</sub>. Concentration of organic layer and drying in vacuum oven provides pure product as a white crystalline solid which needed no further purification (82%). <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>)  $\delta$  12.85 (bs, 1H), 8.08 (d, J = 8.5 Hz, 2H), 7.51 (d, J = 8.5 Hz, 2H), 1.37 (s, 9H).

4,8-Dibromo-2,6-bis(4-(tert-butyl)phenyl)benzo[1,2-d:4,5-d'] bis(oxazole) (26P48Br). This product was prepared according to previous literature procedures using benzoic acid P2.21 Compound was used without further purification or identification. (33%)

4,8-Dibromo-2,6-bis(5-hexylfuran-2-yl)benzo[1,2-d:4,5-d']bis (oxazole) (26F48Br). To an oven dried,  $N_2$  filled round bottom flask equipped with stir bar was added F4 (3 mol eq), an. THF, and an. DMAc. The solution was degassed with N2 for appx. 25 minutes. Afterwards, Yb(OTf)<sub>3</sub> (5 mol%) was added to the flask and the solution was then brought to 40 °C. Br-DAHQ (1 mol eq) is added portion-wise to the solution over a period of 5 minutes. Solution is heated to 60 °C for 24 hours. After cooling to room temperature, the solution is poured into MeOH, filtered and dried to provide the product. Pale yellow solid (77%). <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>)  $\delta$  7.36 (d, J = 3.5, 2H), 6.26 (d, I = 3.5 Hz, 2H), 2.79 (t, I = 7.6, 4H), 1.75 (quintet, I =7.6 Hz, 4H), 1.44-1.28 (m, 12H), 0.94-0.88 (m, 6H). <sup>13</sup>C (126 MHz, CDCl<sub>3</sub>)  $\delta$  162.42, 156.65, 146.32, 139.78, 139.31, 117.65, 108.28, 91.37, 31.47, 28.85, 28.39, 27.72, 22.53, 14.03.

4,8-Dibromo-2,6-bis(5-hexylthiophen-2-yl)benzo[1,2-d:4,5-d'] bis(oxazole) (26T48Br). This compound was prepared analogously to compound 26F48Br using T2. (56%). <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>)  $\delta$  7.85 (d, J = 3.8 Hz, 2H), 6.88 (d, J =3.8 Hz, 2H), 2.90 (t, J = 7.6 Hz, 4H), 1.74 (quintet, J = 7.6 Hz, 4H), 1.46–1.28 (m, 12H), 0.90 (t, J = 7.2 Hz, 6H). <sup>13</sup>C (125 MHz,  $CDCl_3$ )  $\delta$  160.39, 153.71, 146.49, 139.41, 131.55, 125.84, 125.49, 90.95, 31.49, 31.35, 30.44, 28.69, 22.53, 14.04.

## General Suzuki-Miyaura cross-coupling conditions

All equivalence/mole percentage values are in reference to the starting BBO. To a condenser-fitted flask, equipped with stir bar, was added the starting BBO, 3 mol eq of 9, and 5 mol% of PEPPSI-iPr. The flask was purged with argon three times before the addition of 2 M K<sub>2</sub>CO<sub>3</sub> (30 mol eq.) and toluene. The solution was degassed with argon for 15 minutes and allowed to reflux overnight at 120 °C. Upon cooling, the solution was diluted with chloroform, washed with DI water, and separated from the aqueous layer. The organic layer was dried over Na<sub>2</sub>SO<sub>4</sub> and filtered into a flask with silica. Removal of solvent facilitated the formation of solid-load product necessary for column chromatography (hexanes:CHCl3 gradient) to purifying the products. Below are the physical characteristics, percent yields, and characterization data for all compounds using this method:

2,4,6,8-Tetrakis(4-(tert-butyl)phenyl)benzo[1,2-d:4,5-d']bis(oxazole) **(PP).** Shiny-white solid. (61%). TGA<sub>5%</sub>: 438 °C.M.P.: > 240 °C. <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>)  $\delta$  8.41, (d, J = 8.4 Hz, 4H), 8.28 (d, J = 8.4 Hz, 4H), 7.68 (d, I = 8.5 Hz, 4H), 7.56 (d, I = 8.3 Hz, 4H), 1.46 (s, 18H), 1.39 (s, 18H).  $^{13}$ C (126 MHz, CDCl<sub>3</sub>)  $\delta$  163.7, 155.0, 151.1, 146.3, 138.3, 129.9, 129.8, 127.6, 125.8, 125.6, 124.5, 113.8, 35.1. 34.8, 31.4, 31.2. HRMS (ESI) m/z:  $[M + H]^+$  calc'd for C<sub>48</sub>H<sub>52</sub>N<sub>2</sub>O<sub>2</sub>:689.4107; found: 689.4094.

4,8-Bis(4-(tert-butyl)phenyl)-2,6-bis(5-hexylfuran-2-yl)benzo [1,2-d:4,5-d']bis(oxazole) (FP). Shiny, off-white solid (with slight pale-green hue) (63%). TGA<sub>5%</sub>: 340 °C.M.P.: > 240 °C. <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>)  $\delta$  8.27 (d, J = 8.1 Hz, 4H), 7.64 (d, J = 8.1 Hz, 4H), 7.23 (d, J = 3.4 Hz, 2H), 6.21 (d, J = 3.4 Hz, 2H), 2.78 (t, J =7.7 Hz, 4H), 1.75 (quintet, J = 7.6 Hz, 4H), 1.46–1.30 (m, 30H), 0.94 (t, J = 6.3 Hz, 6H). <sup>13</sup>C NMR (126 MHz, CDCl<sub>3</sub>)  $\delta$  161.15, 156.21, 151.05, 145.75, 140.82, 137.96, 129.81, 129.43, 125.60, 115.84, 113.91, 107.72, 77.25, 77.00, 76.74, 34.77, 31.51, 31.36, 28.87, 28.33, 27.69, 22.55, 14.06. HRMS (ESI) m/z: [M + H] calc'd for C<sub>48</sub>H<sub>57</sub>N<sub>2</sub>O<sub>4</sub>: 725.4318; found: 725.4323.

**Materials Advances** Paper

4,8-Bis(4-(tert-butyl)phenyl)-2,6-bis(5-hexylthiophen-2-yl)benzo [1,2-d:4,5-d']bis(oxazole) (TP). Shiny, off-white solid (with slight pale-green hue) (72%). TGA<sub>5%</sub>: 375 °C.M.P.: > 240 °C. <sup>1</sup>H NMR  $(500 \text{ MHz}, \text{CDCl}_3) \delta 8.32 \text{ (d, J} = 8.5 \text{ Hz}, 4\text{H}), 7.79 \text{ (d, J} = 3.8 \text{ Hz}, 2\text{H}),$ 7.64 (d, J = 8.5 Hz, 4H), 6.86 (d, J = 3.8 Hz, 2H), 2.89 (t, J = 7.6 Hz, 4H), 1.75 (quintet, I = 7.5 Hz, 4H), 1.44 (s, 24H), 1.37–1.30 (m, 8H), 0.90 (t, J = 7.1 Hz, 6H). <sup>13</sup>C NMR (126 MHz, CDCl<sub>3</sub>)  $\delta$  159.65, 151.95, 151.02, 146.00, 138.13, 130.12, 129.81, 129.61, 126.94, 125.55, 125.47, 113.41, 77.25, 77.00, 76.74, 34.78, 31.52, 31.48, 31.37, 30.42, 28.73, 22.55, 14.05. HRMS (ESI) m/z: [M + H]<sup>+</sup> calc'd for  $C_{48}H_{57}N_2O_2S_2$ : 757.3861; found: 757.3862.

#### General Stille cross-coupling conditions

All equivalence/mole percentage values are in reference to the starting BBO. To a condenser-fitted flask equipped with stir bar was added the starting BBO, 2.5 mol% of Pd<sub>2</sub>(dba)<sub>3</sub>, and 10 mol% of tri(o-tolyl)phosphine. The flask was purged with argon three times before the addition of corresponding organotin reagent (3 mol eq) and toluene. The solution was degassed with argon for 15 minutes and allowed to reflux overnight at 120 °C. Upon cooling, the solution was diluted with chloroform and stirred in a 1:1 mixture of silica gel:K2CO3 for at least 30 minutes. The solids were removed via vacuum filtration and washed with excess chloroform. To the solution was added fresh silica gel. Removal of solvent facilitated the formation of solid-load product necessary for column chromatography (hexanes:CHCl<sub>3</sub> gradient) to purifying the products. Below are the physical characteristics, percent yields, and characterization data for all compounds using this method:

4,8-Bis(5-hexylfuran-2-yl)-2,6-bis(4-(tert-butyl)phenyl)benzo [1,2-d:4,5-d']bis(oxazole) (PF). Vibrant yellow solid. (61%). TGA<sub>5%</sub>: 350 °C.M.P.: 200–208 °C. <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>)  $\delta$ 8.33 (d, J = 8.1 Hz, 4H), 7.62 (d, J = 3.3 Hz, 2H), 7.58 (d, J = 8.1 Hz, 4H), 6.31 (d, J = 3.3 Hz, 2H), 2.90 (t, J = 7.6 Hz, 4H), 1.91 (quintet, J = 7.7 Hz, 4H), 1.54 (quintet, J = 7.1, 6.4 Hz, 4H), 1.46– 1.35 (m, 26H), 0.93 (t, J = 6.9 Hz, 6H). <sup>13</sup>C NMR (126 MHz,  $CDCl_3$ )  $\delta$  163.92, 157.37, 154.90, 145.97, 143.67, 135.90, 127.55, 125.78, 124.62, 113.15, 107.41, 104.34, 77.24, 76.99, 76.73, 35.08, 31.81, 31.18, 29.08, 28.52, 28.03, 22.62, 14.17. HRMS (ESI) m/z:  $[M + H]^+$  calc'd for  $C_{48}H_{57}N_2O_4$ : 725.4318; found:

4,8-Bis(5-hexylthiophen-2-yl)-2,6-bis(4-(tert-butyl)phenyl)benzo [1,2-d:4,5-d']bis(oxazole) (PT). Golden yellow solid. (63%). TGA<sub>5%</sub>: 360 °C.M.P.: 218–220 °C. <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>)  $\delta$  8.37–8.33 (m, 6H), 7.61 (d, J = 8.5 Hz, 4H), 6.97 (d, J = 3.6 Hz, 2H), 2.97 (t, J = 3.6 Hz, 2H)7.6 Hz, 4H), 1.82 (quintet, J = 7.6 Hz, 4H), 1.51–1.45 (m, 4H), 1.43– 1.34 (m, 28H), 0.95–0.91 (t, J = 7.0 Hz, 6H). <sup>13</sup>C NMR (126 MHz,  $CDCl_3$ )  $\delta$  163.30, 154.99, 147.96, 144.37, 136.53, 131.97, 128.82, 127.66, 125.86, 124.65, 124.42, 107.80, 35.10, 31.75, 31.66, 31.20, 30.26, 28.93, 22.66, 14.13. HRMS (ESI) m/z:  $[M + H]^+$  calc'd for C<sub>48</sub>H<sub>57</sub>N<sub>2</sub>O<sub>2</sub>S<sub>2</sub>: 757.3861; found: 757.3876.

## Device fabrication and characterization

OLED devices were fabricated on pre-patterned ITO (100 nm)/ glass substrates with 20  $\Omega$  sq<sup>-1</sup> resistance (Ossila, Ltd.). Substrates were cleaned by sonicating in Mucasol, water  $(2\times)$ ,

acetone, isopropanol and finally dried in an oven for at least one hour. Substrates were then subject to 15 minutes of UV-ozone curing to aide in hole-injection. Next, PEDOT:PSS (Heraeus Clevios P VP AI 4083) was spin-coated onto each substrate (3500 RPM, 2 minutes) followed by annealing at 120 °C for 20 minutes under a nitrogen atmosphere, producing an appx. 35 nm layer. The active layer solution (conc.: 9 mg mL<sup>-1</sup>) composed of a mixed-host system (with 5% w/w dopant) dissolved in chlorobenzene. The host matrix was a 1:1 ratio of 26DCzPPY:TCTA. Solutions were allowed to stir at 50 °C for at least one hour and filtered prior to solution processing. The active layer was spin-coated on top of the PEDOT:PSS at 4000 RPM for 15 seconds and then annealed at 120 °C for 10 minutes. Substrates were then transferred to a thermal evaporator where TmPyPB (30 nm;  $0.5 \text{ Å s}^{-1}$ ), LiF (1 nm;  $0.1 \text{ Å s}^{-1}$ ), and Al (100 nm;  $2 \text{ Å s}^{-1}$ ) were sequentially evaporated at  $10^{-6}$  Torr. Finally, substrates were coated with a UV-curing epoxy and glass coverslip and cured at 365 nm for 25 minutes to perform measurements in ambient conditions. OLED electrical properties were characterized using an Ossila Ltd. Lifetime System. Electroluminescence was recorded using a Konica Minolta LS-160 luminance meter and electroluminescent spectra were recorded using an Ocean Insight HR2000+ ES spectrometer, calibrated using a HL-3-plus light source. Tapping-mode AFM measurements were made using a Bruker Dimension 3000 microscope.

## Author contributions

David Wheeler: conceptualization, methodology, investigation, writing - original draft, writing - review & editing, and visualization. Shambhavi Tannir: investigation, writing - revision writing - review & editing. Evan Smith: investigation and data curation. Aimeé Tomlinson: conceptualization, methodology, investigation, resources, writing - original draft, writing review & editing, visualization and funding acquisition. Malika Jeffries-EL: conceptualization, methodology, investigation, writing - original draft, writing - review & editing, visualization supervision, project administration and funding acquisition.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

We thank the National Science Foundation (CHE-1808402, and CHE-1808414) as well as supercomputer allocation from XSEDE (DMR-160146) for financial support of this work. We also would like to thank Dr. Paul Ralifo and Dr. Norman Lee of the Boston University Chemistry Instrumentation Center for NMR and HR-MS access and measurements (respectively), Professor Allison Dennis for fluorimeter/integrating sphere access for quantum yield measurements, Dr. Paul Mak for profilometry access, and Dr. Anlee Krupp for AFM access. We also thanks Professors Joseph Shinar, Dr. Ruth Shinar, Mr. Michael Fralaide and Mr.

Erik Dykstra from Iowa State University for help with EQE

calculations.

## Notes and references

**Paper** 

- 1 C. Lee, S. Lee, G.-U. Kim, W. Lee and B. J. Kim, Chem. Rev., 2019, 119, 8028-8086.
- 2 L. Ying, F. Huang and G. C. Bazan, Nat. Commun., 2017, 8, 14047.
- 3 Y.-W. Su, Y.-C. Lin and K.-H. Wei, J. Mater. Chem. A, 2017, 5, 24051-24075.
- 4 D. T. Christiansen, S. Ohtani, Y. Chujo, A. L. Tomlinson and J. R. Reynolds, Chem. Mater., 2019, 31, 6841-6849.
- 5 P. M. Beaujuge and J. R. Reynolds, Chem. Rev., 2010, 110, 268-320.
- 6 G. Yang, Y.-M. Zhang, Y. Cai, B. Yang, C. Gu and S. X.-A. Zhang, Chem. Soc. Rev., 2020, 49, 8687-8720.
- 7 A. M. Österholm, D. E. Shen and J. R. Reynolds, in Conjugated Polymers: Properties, Processing, and Applications, ed. J. R. Reynolds, B. C. Thompson and T. A. Skotheim, CRC Press, 4th edn, 2019, ch. 6, DOI: 10.1201/9780429190520chapter-6.
- 8 D. T. Christiansen, A. L. Tomlinson and J. R. Reynolds, J. Am. Chem. Soc., 2019, 141, 3859-3862.
- 9 M. Zhu and C. Yang, Chem. Soc. Rev., 2013, 42, 4963-4976.
- 10 X. Yang, X. Xu and G. Zhou, J. Mater. Chem. C, 2015, 3, 913-944.
- 11 J. H. Burroughes, D. D. C. Bradley, A. R. Brown, R. N. Marks, K. Mackay, R. H. Friend, P. L. Burns and A. B. Holmes, Nature, 1990, 347, 539-541.
- 12 H. Gorter, M. J. J. Coenen, M. W. L. Slaats, M. Ren, W. Lu, C. J. Kuijpers and W. A. Groen, Thin Solid Films, 2013, 532,
- 13 S.-J. Zou, Y. Shen, F.-M. Xie, J.-D. Chen, Y.-Q. Li and J.-X. Tang, Mater. Chem. Front., 2020, 4, 788-820.
- 14 J. Han and H.-J. Suk, J. Infect. Dis., 2019, 20, 31-38.
- 15 D. Wang, C. Cheng, T. Tsuboi and Q. Zhang, CCS Chem., 2020, 2, 1278-1296.
- 16 D. Y. Kondakov, W. C. Lenhart and W. F. Nichols, J. Appl. Phys., 2007, 101, 024512.
- 17 C.-Y. Chan, M. Tanaka, Y.-T. Lee, Y.-W. Wong, H. Nakanotani, T. Hatakeyama and C. Adachi, Nat. Photonics, 2021, **15**, 203–207.
- 18 S. O. Jeon, K. H. Lee, J. S. Kim, S.-G. Ihn, Y. S. Chung, J. W. Kim, H. Lee, S. Kim, H. Choi and J. Y. Lee, Nat. Photonics, 2021, 15, 208-215.
- 19 B. C. Tlach, A. L. Tomlinson, A. G. Ryno, D. D. Knoble, D. L. Drochner, K. J. Krager and M. Jeffries-EL, J. Org. Chem., 2013, 78, 6570-6581.
- 20 A. J. Zucchero, P. L. McGrier and U. H. F. Bunz, Acc. Chem. Res., 2010, 43, 397-408.
- 21 D. L. Wheeler, A. V. Diodati, A. L. Tomlinson and M. Jeffries-EL, ACS Omega, 2020, 5, 12374-12384.
- 22 J. Lim, T. A. Albright, B. R. Martin and O. Š. Miljanić, J. Org. Chem., 2011, 76, 10207-10219.

- 23 J. E. Klare, G. S. Tulevski and C. Nuckolls, Langmuir, 2004, 20, 10068-10072.
- 24 J. E. Klare, G. S. Tulevski, K. Sugo, A. de Picciotto, K. A. White and C. Nuckolls, J. Am. Chem. Soc., 2003, 125, 6030-6031.
- 25 M. A. Saeed, H. T. M. Le and O. Š. Miljanić, Acc. Chem. Res., 2014, 47, 2074-2083.
- 26 A. A. Burney-Allen, J. Shaw, D. L. Wheeler, L. Diodati, V. Duzhko, A. L. Tomlinson and M. Jeffries-EL, Asian J. Org. Chem., 2021, 10, 215-223.
- 27 R. C. Evers, F. E. Arnold and T. E. Helmeniak, Macromolecules, 1981, 14, 925-930.
- 28 Q. Fu, H. Zhang, B. Song, X. Liu, Q. Zhuang and Z. Han, J. Appl. Polym. Sci., 2011, 121, 1734-1739.
- 29 S. J. Krause, T. B. Haddock, D. L. Vezie, P. G. Lenhert, W. F. Hwang, G. E. Price, T. E. Helminiak, J. F. O'Brien and W. W. Adams, Polymer, 1988, 29, 1354-1364.
- 30 D. B. Roitman, R. A. Wessling and J. McAlister, Macromolecules, 1993, 26, 5174-5184.
- 31 M. M. Alam and S. A. Jenekhe, Chem. Mater., 2002, 14, 4775-4780.
- 32 R. Chavez III, M. Cai, B. Tlach, D. L. Wheeler, R. Kaudal, A. Tsyrenova, A. L. Tomlinson, R. Shinar, J. Shinar and M. Jeffries-EL, J. Mater. Chem. C, 2016, 4, 3765-3773.
- 33 X. Yin, T. Zhang, Q. Peng, T. Zhou, W. Zeng, Z. Zhu, G. Xie, F. Li, D. Ma and C. Yang, J. Mater. Chem. C, 2015, 3, 7589-7596.
- 34 J. J. Intemann, E. S. Hellerich, M. D. Ewan, B. C. Tlach, E. D. Speetzen, R. Shinar, J. Shinar and M. Jeffries-EL, J. Mater. Chem. C, 2017, 5, 12839-12847.
- 35 J. J. Intemann, E. S. Hellerich, B. C. Tlach, M. D. Ewan, C. A. Barnes, A. Bhuwalka, M. Cai, J. Shinar, R. Shinar and M. Jeffries-EL, Macromolecules, 2012, 45, 6888-6897.
- 36 E. S. Hellerich, J. J. Internann, M. Cai, R. Liu, M. D. Ewan, B. C. Tlach, M. Jeffries-EL, R. Shinar and J. Shinar, J. Mater. Chem. C, 2013, 1, 5191-5199.
- 37 O. Gidron, A. Dadvand, Y. Sheynin, M. Bendikov and D. F. Perepichka, Chem. Commun., 2011, 47, 1976-1978.
- 38 O. Gidron and M. Bendikov, Angew. Chem., Int. Ed., 2014, 53, 2546-2555.
- 39 S. S. Zade, N. Zamoshchik and M. Bendikov, Acc. Chem. Res., 2010, 44, 14-24.
- 40 R. D. McCullough, Adv. Mater., 1998, 10, 93-116.
- 41 I. Osaka and R. D. McCullough, Acc. Chem. Res., 2008, 41, 1202-1214.
- 42 B. S. Kim and J. Y. Lee, Adv. Funct. Mater., 2014, 24, 3970-3977.
- 43 Y. J. Doh, J. S. Park, W. S. Jeon, R. Pode and J. H. Kwon, Org. Electron., 2012, 13, 586-592.
- 44 S.-K. Kim, B. Yang, Y. Ma, J.-H. Lee and J.-W. Park, J. Mater. Chem., 2008, 18, 3376-3384.
- 45 Y. Yu, Z. Wu, Z. Li, B. Jiao, L. Li, L. Ma, D. Wang, G. Zhou and X. Hou, J. Mater. Chem. C, 2013, 1, 8117-8127.
- 46 C.-C. Huang, M.-M. Xue, F.-P. Wu, Y. Yuan, L.-S. Liao and M.-K. Fung, Molecules, 2019, 24, 353-362.

- Pachariyangkun, P. Wongkaew, T. Sudyoadsuk, S. Namuangruk and V. Promarak, Dyes Pigm., 2021, 186, 109065.
- 48 Y. Tan, Z. Wang, C. Wei, Z. Liu, Z. Bian and C. Huang, Org. Electron., 2019, 69, 77-84.
- 49 Z. Li, G. Gan, Z. Ling, K. Guo, C. Si, X. Lv, H. Wang, B. Wei and Y. Hao, Org. Electron., 2019, 66, 24-31.
- 50 J. Santos, J. H. Cook, H. A. Al-Attar, A. P. Monkman and M. R. Bryce, J. Mater. Chem. C, 2015, 3, 2479-2483.
- 51 J. F. Mike, A. J. Makowski and M. Jeffries-EL, Org. Lett., 2008, **10**, 4915–4918.
- 52 Y. Qiu, A. Fortney, C.-H. Tsai, M. A. Baker, R. R. Gil, T. Kowalewski and K. J. T. Noonan, ACS Macro Lett., 2016,
- 53 B. Shaik, J. H. Park, T. K. An, Y. R. Noh, S. B. Yoon, C. E. Park, Y. J. Yoon, Y.-H. Kim and S.-G. Lee, Tetrahedron, 2013, 69, 8191-8198.