


Cite this: *Nanoscale*, 2023, **15**, 19792

Received 31st July 2023,  
Accepted 20th November 2023  
DOI: 10.1039/d3nr03774f  
rsc.li/nanoscale

# Synergistic or antagonistic effect of lanthanides on Rose Bengal photophysics in upconversion nanohybrids?†

Juan Ferrera-González,  María González-Béjar \* and Julia Pérez-Prieto \*

A nanohybrid made of a xanthenic dye, rose bengal, grafted to an ytterbium and erbium codoped upconversion nanoparticle (UCNP) served as a proof-of-concept to evaluate the fundamental mechanisms which govern the dye photophysics upon interaction with the UCNPs. Both photoactive lanthanides strongly influence the singlet and triplet excited states of rose bengal.

## Introduction

Upconversion nanoparticles (UCNPs) are nanoparticles able to convert low energy photons into higher energy photons. The process, termed upconversion (UC), occurs due to the unique properties of photoactive lanthanide ions ( $\text{Ln}^{3+}$ ), which are the dopants of a transparent low-phonon energy matrix. UC is a nonlinear phenomenon and, usually, gives rise to multiple long-lifetime narrow emission bands in the ultraviolet-visible-near infrared (UV-vis-NIR) region upon NIR excitation.<sup>1,2</sup>

Furthermore, upconversion nanohybrids (UCNHs), which combine UCNPs and photoactive species (e.g., dyes, organometallic complexes, or other photoactive nanoparticles) have been used for applications as sensors and bioimaging or therapeutic agents (photothermal, photodynamic, chemotherapy, radiotherapy and so on).<sup>3–9</sup> Often, the photophysical interaction of both constituents in the UCNHs gives rise to an additive or synergistic effect to improve the optical features or generate new ones.

Most of the UCNHs reported so far include chromophores (usually organic dyes) and use energy transfer (trivial or resonant) processes which occur from the  $\text{Ln}^{3+}$  upconversion emission in the UCNPs to the chromophore (NIR sensitization of the chromophore) or *vice versa* (dye-sensitized UCNPs) by

selective excitation of the desired counterpart.<sup>10–14</sup> Some UCNHs, upon selective excitation of the UCNPs and subsequent energy transfer to the chromophore, can generate triplet states after intersystem crossing. This chromophore can then react with oxygen to produce reactive oxygen species (ROS).<sup>4,15</sup> Among the chromophores used to fabricate UCNHs are pyropheophorbide a,<sup>16</sup> cationic porphyrin TMPyP4,<sup>17</sup> diiodo-BODIPY,<sup>18</sup> Rose Bengal (RB),<sup>19</sup> methylene blue,<sup>20</sup> hypericin,<sup>21</sup> chlorine e6,<sup>22</sup> and merocyanine 540.<sup>23</sup>

Great efforts have been made to study, model and improve the energy transfer process from the UCNPs  $\text{Ln}^{3+}$  doping to the chromophore.<sup>11,24–30</sup> More than 5000 research articles about UCNHs composed of UCNPs and dyes have been already published,<sup>‡</sup> but only five of them analyzed experimentally the effect of  $\text{Ln}^{3+}$  on the dye excited state photophysics. It is desirable to gain a deeper understanding of the effect that the photoactive lanthanide doping of the UCNPs has on the photophysical properties of chromophores. In this context, it was reported that the presence of heavy lanthanides, in particular  $\text{Gd}^{3+}$ , in the UCNPs favored the intersystem crossing of a dye anchored to the UCNPs surface (IR-806) through the heavy atom effect, eventually leading to dye triplet formation.<sup>31</sup> Later, the enhancement of intersystem crossing was confirmed for other lanthanide cations ( $\text{Tb}^{3+}$ ,  $\text{Eu}^{3+}$ ,  $\text{Gd}^{3+}$  and  $\text{Yb}^{3+}$ ) on films of  $\text{Ln}^{3+}$ -doped nanoparticles with aromatic molecules; remarkably, this enhancement was not only linked to the heavy atom effect, but also to cations with unpaired 4f electrons (dye photophysics remained identical for  $\text{Y}^{3+}$  and  $\text{Lu}^{3+}$  doped nanoparticles). Moreover, heavy lanthanides with

Instituto de Ciencia Molecular (ICMol), Departamento de Química Orgánica, Universitat de València, C/ Catedrático José Beltrán, 2, Paterna, Valencia 46980, Spain. E-mail: maria.gonzalez@uv.es, julia.perez@uv.es

†Electronic supplementary information (ESI) available: Materials and methods, UCNPs TEM images, UCNPs ICP-MS analysis, absorption of RB, attenuation of UCNPs@RB, RB concentration study in DMF, calculation of RB molecules per UCNPs, TAS spectra and kinetics of RB and UCNPs@RB, scheme of RB photophysical processes under  $\text{N}_2$  and air,  $k_q(\text{O}_2)$  Stern–Volmer plot, NIR-II emission kinetics, upconversion and downshifting emission kinetics of UCNPs and UCNPs@RB and their fitting parameters. See DOI: <https://doi.org/10.1039/d3nr03774f>

‡Search performed in Web of Science (Clarivate Analytics) reported 5242 results with the following input data: database: all; type of document: article; topic: upconversion nanoparticles; keywords should include: upconverting nanoparticles, nanohybrid, nanosystem, nanoplateform, nanostructure, heterostructure; keywords must include: dye. Date of search: 2023-10-11.



unpaired electrons also enabled the observation of the triplet exciton absorption transition ( $S_0 \rightarrow T_n$ ) and the triplet state absorption deactivation lifetime decreased with respect to that of the pristine dye due to energy transfer to the  $\text{Ln}^{3+}$  ions.<sup>32</sup> Afterwards, by knowing the effect that some lanthanides have on the intersystem crossing of dyes, a smart UCNH was developed to enable sensitization of a lanthanide with no intermediate energy levels ( $\text{Tb}^{3+}$  and  $\text{Eu}^{3+}$ ) in a core-shell-shell UCNH through dye triplet excited states.<sup>33</sup> More recent research attributes, once again, the heavy atom effect as responsible for the intersystem crossing enhancement.<sup>34,35</sup> Although the exact mechanism behind these observations is still controversial, all these publications clearly demonstrate that  $\text{Ln}^{3+}$  in the UCNH influences the dye photophysics.

Moreover, the restriction of movement of the dye anchored to the surface, the interaction with the surface<sup>36</sup> and the potential dye aggregation<sup>37,38</sup> raise serious doubts as to whether its behavior is the same as when it is free in solution. Consequently, dye photophysics can change considerably and should be reported for each UCNH.

Herein, we have selected a colloidal UCNH, commonly used in the field, as a model to evaluate the photophysical processes and phenomena that take place between its counterparts. Specifically, the  $\text{UC}_{\text{Er}}@RB$  UCNH is composed of  $\beta\text{-NaYF}_4\text{:Yb}^{3+}(20\%),\text{Er}^{3+}(2\%)$ , a UCNH of *ca.* 20 nm and RB adsorbed on the surface.  $\text{UC}_{\text{Er}}@RB$  has been selected based on the relatively high resonant energy transfer from  $\text{Er}^{3+}$  to RB and its reproducible and easy synthesis.<sup>39</sup> In this system, RB absorption overlaps the main UC emission of  $\text{Er}^{3+}$  (520–540 nm). Moreover, RB photophysics is well known and presents a high intersystem crossing quantum yield (>90%)<sup>40</sup> and  $^1\text{O}_2$  generation (68–80%).<sup>41</sup>

UCNHs made of UCNPs and RB have been investigated in the past.<sup>19,42–45</sup> Most of them detected  $^1\text{O}_2$  by using optical probes (*e.g.*, 1,3-diphenylisobenzofuran, DPBF) or by detecting  $^1\text{O}_2$  phosphorescence.<sup>8,19</sup> Core-shell structures with increased concentrations of donor lanthanides in the shell are beneficial for resonant energy transfer to dyes.<sup>24</sup> Also, the thickness of a silica shell coating the UCNH ( $\text{NaYF}_4\text{:Yb}^{3+}(20\%),\text{Er}^{3+}(2\%)$ ) influences the energy transfer to RB on the surface.<sup>45</sup> The distance exerted an opposite influence between UC luminescence (reducing surface effects and solvent deactivation) and the energy transfer efficiency. The best energy transfer occurred with a 6 nm coating, leading to an emission of RB sensitized by UCNH with a lifetime on the microsecond scale.

All this considered, there is still an important lack of knowledge about how the photophysics of chromophores can be affected when anchored to the UCNH surface in colloidal dispersions.

This work presents a comparative analysis between free RB and RB in a UCNH and focusses on obtaining the most com-

plete overview of the photophysical processes that could take place between the photoactive counterparts in  $\text{UC}_{\text{Er}}@RB$ . It is of fundamental importance to understand the overall photophysics of the nanohybrid and develop nanomaterials with appropriate photoactive properties.

Does the combination of RB with UCNPs generate a synergistic or an antagonistic effect on RB photophysics in these “well-known” UCNHs?

## Results and discussion

### Nanohybrid synthesis and characterization

One batch of  $\beta\text{-NaYF}_4\text{:Yb}^{3+}(28\%),\text{Er}^{3+}(3\%)$  UCNPs were synthesized by thermal decomposition (see Table S1†).<sup>46</sup> The hexagonal prisms had a size of  $21.0 \pm 0.8 \times 18.9 \pm 0.7$  nm (Fig. S1†). Subsequently, the UCNPs were treated with  $\text{NOBF}_4$  to eliminate oleate ligands from the surface,<sup>47</sup> giving rise to oleate-free UCNPs ( $\text{UC}_{\text{Er}}$ ). Then,  $\text{UC}_{\text{Er}}$  was exposed to an excess of RB (42 mM) in DMF under shaking for 24 hours, followed by washing with DMF until the supernatant showed negligible RB absorption. The resulting UCNHs,  $\text{UC}_{\text{Er}}@RB$ , were redispersed in DMF.

Dynamic light scattering (DLS) measurements showed that the average hydrodynamic diameter ( $D_h$ ) of  $\text{UC}_{\text{Er}}@RB$  increases slightly (either by intensity or number) (Fig. S2:†  $27.9 \pm 0.3$  and  $86.3 \pm 0.8$  nm for  $\text{UC}_{\text{Er}}$  and  $\text{UC}_{\text{Er}}@RB$ , respectively). This reflected the UCNH coverage with the dye. Moreover, the average polydispersity index (PDI) for  $\text{UC}_{\text{Er}}$  and  $\text{UC}_{\text{Er}}@RB$  was  $0.238 \pm 0.015$  and  $0.344 \pm 0.006$ , respectively. The acceptable monodispersity of the samples supports that the degree of RB functionalization among UCNPs is fairly homogeneous.

### Photophysics of $\text{UC}_{\text{Er}}@RB$

The photophysical interaction between  $\text{UC}_{\text{Er}}$  and RB in  $\text{UC}_{\text{Er}}@RB$  has been studied and is presented in the next two sections. *N,N*-Dimethylformamide (DMF) has been the solvent of choice because it allows the preparation of concentrated, low-scattering dispersions of  $\text{UC}_{\text{Er}}@RB$ . Fig. 1 shows the energy diagrams for the photophysical processes that can be observed for  $\text{UC}_{\text{Er}}@RB$  exciting either the dye ( $\lambda_{\text{exc}} = 560$  nm) or the UCNH ( $\lambda_{\text{exc}} = 980$  nm).

### Photophysics of RB in the UCNH


The photophysical properties of RB in the  $\text{UC}_{\text{Er}}@RB$  dispersion were studied and compared with those of RB in solution to evaluate the effect that aggregation and photoactive lanthanide doping of  $\text{UC}_{\text{Er}}$  have on the photophysical properties of RB. The contribution of each excited state is summarized in Table 1. Energy transfer from RB to  $\text{UC}_{\text{Er}}$  in the UCNH is also discussed.

**Ground and singlet states of RB.** The absorption and emission spectra of RB and  $\text{UC}_{\text{Er}}@RB$  in DMF are shown in Fig. 2a. Both present the characteristic absorption band with a shoulder, but the absorption band of RB in  $\text{UC}_{\text{Er}}@RB$  is wider than that of RB and the absorption maximum ( $\lambda_{\text{max}}$ ) under-

† Set up:  $\text{O}_2$ -saturated  $\text{D}_2\text{O}$  colloidal dispersion with no reported concentration; excitation: a CW 980 nm laser diode with no reported power density; detection: a liquid nitrogen cooled InGaAs detector.





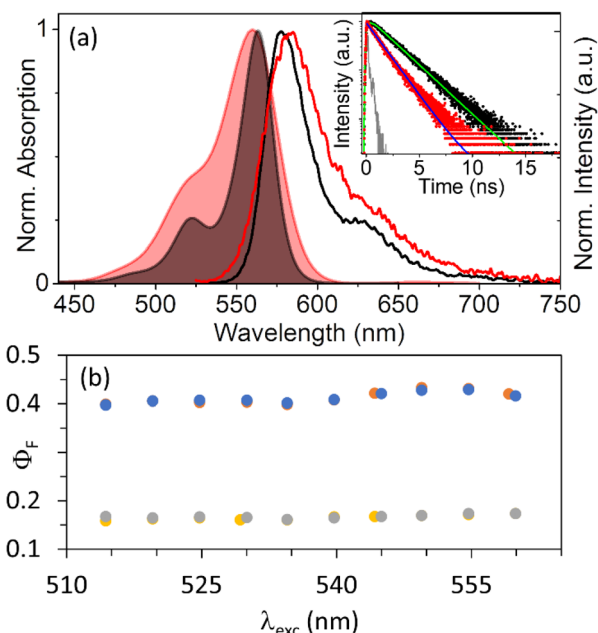

**Fig. 2** (a) Normalized absorption (colored areas) and emission (lines, λ<sub>exc</sub> = 522 nm) of RB (black) and UC<sub>Er</sub>@RB (red). Raw attenuation data are shown in Fig. S3†. Inset: fluorescence lifetime kinetics (dots) and fitting (lines) of RB (black, 2.7 × 10<sup>−7</sup> M) and UC<sub>Er</sub>@RB (red, <1 mg mL<sup>−1</sup>) under N<sub>2</sub>; λ<sub>exc</sub> = 560 nm, NKT laser 5.5 MHz; λ<sub>em</sub> = 580 nm. (b) Fluorescence quantum yield of RB under air (blue dots) and N<sub>2</sub> (orange dots) and UC<sub>Er</sub>@RB under air (grey dots) and N<sub>2</sub> (yellow dots) versus excitation wavelength (A = 0.1 at 560 nm).

quench the singlet excited state <sup>1</sup>RB. This can be attributed to different factors. One of them is RB aggregation, as mentioned above. Additionally, an improvement in the intersystem crossing efficiency when RB is anchored to the UCNH surface could be due to the heavy atom effect of the lanthanides,<sup>31,65</sup> or/and an energy transfer from <sup>1</sup>RB to the lanthanides (despite their low absorption coefficient). Both have been studied and are discussed in the following sections (see RB triplet state, internal conversion and energy transfer).

**Internal conversion.** The internal conversion quantum yield (Φ<sub>ic</sub>) for free RB was estimated to be 0.13, according to eqn (1) valid for non-reactive molecules.<sup>66</sup>

$$\Phi_F + \Phi_{ISC} + \Phi_{IC} = 1 \quad (1)$$

In contrast, the Φ<sub>ic</sub> value of RB in UC<sub>Er</sub>@RB was 0.48. A lower Φ<sub>ic</sub> than the one obtained for free RB was expected for RB in UC<sub>Er</sub>@RB, because RB was anchored to the UCNH surface. The hypotheses of <sup>1</sup>RB singlet deactivation due to the heavy atom effect of the UCNH and dye aggregation would result in an increase in the Φ<sub>isc</sub>. Clearly this was not the case, thus leaving a possible energy transfer from <sup>1</sup>RB to Ln<sup>3+</sup> as the preferred explanation. In this context, a new term (η<sub>et</sub>Φ<sub>et</sub>), which considers the efficiency of the energy transfer (η<sub>et</sub>) and the energy transfer quantum yield to the Ln<sup>3+</sup> (Φ<sub>et</sub>), should be added to eqn (1). If the Φ<sub>ic</sub> values of RB in solution and in UC<sub>Er</sub>@RB were identical, a contribution of 0.35 may be attrib-

uted to η<sub>et</sub>Φ<sub>et</sub>. This photophysical pathway is discussed in the energy transfer section.

**RB triplet state.** Nanosecond-laser flash photolysis was used to register transient absorption spectra (Fig. 3a). The photophysical behavior of RB in DMF is similar to that reported in acetonitrile (ACN).<sup>40</sup> The RB triplet excited state (<sup>3</sup>RB) was generated a few nanoseconds after the laser pulse and exhibited absorption bands at ca. 380, 470 and 610 nm. In the case of RB in solution, <sup>3</sup>RB subsequently evolved into the RB radical anion (RB<sup>•−</sup>), which absorbs at ca. 440 nm and is long-lived (450 μs) (Fig. 3a). In contrast, when exciting RB in UC<sub>Er</sub>@RB, <sup>3</sup>RB was exclusively generated, i.e., radical anion formation was clearly prevented. In a similar way, Baptista *et al.*<sup>67</sup> observed that when methylene blue aggregates were excited, they dissociated and formed a triplet identical to that of the monomer. Likewise, Kamat *et al.*<sup>37</sup> observed that rhodamine 6G aggregates on the surface of SiO<sub>2</sub> colloids formed only the triplet of the dye.

The kinetics of the singlet bleaching at 560 nm (τ<sub>BI</sub>) matched well with the absorption of the triplet at 610 nm (τ<sub>T</sub> = 240–260 μs) and was very similar for free RB and RB in the UCNH (Fig. S6† and Table 1). However, the bleaching of RB at 560 nm was much weaker when RB is in the UCNH due to scattering and fitted a biexponential equation.

The intersystem crossing (or triplet formation) quantum yield (Φ<sub>isc</sub>) of RB in UC<sub>Er</sub>@RB was slightly lower (0.35), i.e., less <sup>3</sup>RB was formed as compared to RB (0.45, Table 1). As expected, RB Φ<sub>isc</sub> values in aprotic polar solvents, such as DMF here reported or ACN (Φ<sub>isc</sub> = 0.4),<sup>68</sup> were lower than in protic polar solvents (Φ<sub>isc</sub> > 90%).<sup>40</sup>

Moreover, the rate constant for O<sub>2</sub> quenching of <sup>3</sup>RB, k<sub>q</sub>(O<sub>2</sub>) (Table 1 and Fig. S7†), revealed a fast process, close to a diffusion-controlled mechanism (k<sub>diff</sub>(DMF) ≈ 8 × 10<sup>9</sup> M<sup>−1</sup> s<sup>−1</sup>).<sup>¶</sup> Remarkably, this process was ca. three times slower for <sup>3</sup>RB in UC<sub>Er</sub>@RB, probably due to the restricted mobility of RB when grafted to the UCNH and the formation of aggregates, which limited the diffusion rate.

Laser induced emission measurements showed that RB exhibits room temperature phosphorescence together with thermally activated delayed fluorescence, as previously reported for other xanthenic dyes, such as eosin.<sup>69</sup> The phosphorescence of <sup>3</sup>RB under N<sub>2</sub> began at ca. 670 nm and extended to ca. 1300 nm (*vide infra*) with a maximum at ca. 750 nm (755 and 753 nm for RB and UC<sub>Er</sub>@RB, respectively; Fig. 3b). The phosphorescence intensity of RB in the UCNH was weaker and its lifetime (τ<sub>p</sub>) was shorter than that of RB (Fig. 3c and Table 1). These results point out that there are other mechanisms that deactivate the <sup>3</sup>RB in the UCNH as compared to those of RB in solution. In addition, the weaker intensity of the delayed fluorescence of RB in UC<sub>Er</sub>@RB emphasized, once again, the existence of a <sup>1</sup>RB deactivation process.

¶ Calculated from equation k<sub>diff</sub> = 8RT · 10<sup>3</sup> / (3η), R being the gas constant, T being the temperature and η being the viscosity of the solvent.<sup>75</sup>







**Fig. 3** (a) Transient absorption spectra of (top) RB and (down) UC<sub>Er</sub>@RB recorded 20 ns (black) and 450 μs (blue) after the laser pulse under N<sub>2</sub> ( $\lambda_{\text{exc}} = 560$  nm,  $A = 0.28$  at 560 nm). (b) Laser-induced emission spectra of RB solution (black) and UC<sub>Er</sub>@RB dispersion (red,  $A = 0.28$  at 560 nm) 100 ns after the laser pulse ( $\lambda_{\text{exc}} = 560$  nm) showing the phosphorescence and delayed emission of RB. (c) Kinetic profiles (dots) and fitting (lines) of RB (black,  $1.6 \times 10^{-5}$  M) and UC<sub>Er</sub>@RB (red, 5 mg mL<sup>-1</sup>) under N<sub>2</sub> ( $\lambda_{\text{exc}} = 560$  nm,  $\mu\text{F2}$  lamp;  $\lambda_{\text{em}} = 750$  nm). Grey dots represent the IRF.

The NIR emission spectrum of RB (Fig. 4) showed that the tail of the phosphorescence lengthened up to ca. 1300 nm, while under air it was almost completely deactivated and the emission band characteristic of <sup>1</sup>O<sub>2</sub> phosphorescence centered at 1275 nm was observed (scheme in Fig. S8†).

**Energy transfer from RB to UC<sub>Er</sub> in the UCNH.** When RB in the UCNH was selectively excited, two intense new bands centered at 975 and 1550 nm were registered together with RB phosphorescence (Fig. 4). The band at 975 nm is attributed to the Yb<sup>3+</sup> <sup>2</sup>F<sub>5/2</sub> → <sup>2</sup>F<sub>7/2</sub> transition (the Er<sup>3+</sup> <sup>4</sup>I<sub>11/2</sub> → <sup>4</sup>I<sub>15/2</sub> transition could play a minor role due to the lower doping). The band at 1550 nm can be unequivocally attributed to the Er<sup>3+</sup> <sup>4</sup>I<sub>13/2</sub> → <sup>4</sup>I<sub>15/2</sub> transition.


Upon energy transfer from RB, <sup>4</sup>F<sub>9/2</sub> (655 nm) would be most likely the populated energy level of Er<sup>3+</sup>. Control experiments showed that the emission bands at 975 and 1550 nm were weaker when exciting the UC<sub>Er</sub> at 655 nm than the UC<sub>Er</sub>@RB nanohybrid at 560 nm (Table S3†). Therefore, these

bands have been generated due to an efficient antenna effect from RB to the photoactive lanthanide ions in the UCNH (Fig. 1a).

Moreover, the emission intensities of these NIR bands at 975 nm (Yb<sup>3+</sup> emission and <sup>3</sup>RB phosphorescence) and 1550 nm (Er<sup>3+</sup> emission) were greatly influenced by the atmosphere (N<sub>2</sub>/air).

The emission bands registered under air originated exclusively from an energy transfer process from <sup>1</sup>RB (pathway i in Fig. 1a), since <sup>3</sup>RB was efficiently deactivated under air (calculated O<sub>2</sub> quenching efficiency >0.99). Accordingly, the emission bands under an inert atmosphere are due to the energy transfer from <sup>1</sup>RB (46%) and <sup>3</sup>RB (54%) to the photoactive lanthanides (pathways i and ii in Fig. 1a). This result is consistent with ca. 50% reduction of the RB fluorescence and phosphorescence lifetimes.

The emission kinetic profiles at 975 nm and 1550 nm under N<sub>2</sub> were fitted to a biexponential decay function. At

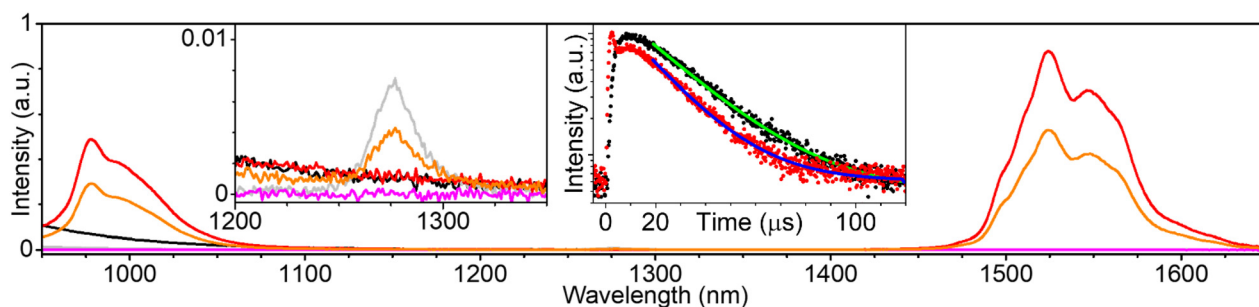

**Fig. 4** NIR emission spectra of RB ( $1.6 \times 10^{-5}$  M) under N<sub>2</sub> (black) and air (grey), UC<sub>Er</sub> (5 mg mL<sup>-1</sup>) under N<sub>2</sub> (pink) and UC<sub>Er</sub>@RB (5 mg mL<sup>-1</sup>) under N<sub>2</sub> (red) and air (orange); ( $\lambda_{\text{exc}} = 560$  nm). RB solution and UC<sub>Er</sub>@RB dispersion have identical absorbance (1.34 at 560 nm). Insets: (left) detail of the NIR emission spectra and (right) <sup>1</sup>O<sub>2</sub> emission deactivation at 1275 nm of RB (black,  $1.6 \times 10^{-5}$  M) and UC<sub>Er</sub>@RB (red, 5 mg mL<sup>-1</sup>) under air ( $\lambda_{\text{exc}} = 560$  nm,  $\mu\text{F2}$  lamp).



975 nm, the biexponential behavior was due to the co-detection of two species:  $\text{Yb}^{3+}$  and  $^3\text{RB}$ , a short one of 52  $\mu\text{s}$  (65%) and a long one of 171  $\mu\text{s}$  (35%) attributed to  $^3\text{RB}$  phosphorescence. In fact, under air the kinetic profile fitted to a mono-exponential decay (48  $\mu\text{s}$ ; Fig. S9 and Table S4†). Similarly, at 1550 nm,  $\text{Er}^{3+}$  emission presented two components; the shortest component was quenched under air (209  $\mu\text{s}$  versus 305  $\mu\text{s}$ ; Fig. S9 and Table S4†), again highlighting the participation of the  $^3\text{RB}$  in the process.

In the presence of air,  $^1\text{O}_2$  phosphorescence was observed at 1275 nm with the characteristic lifetime in DMF (19–23  $\mu\text{s}$ ; inset of Fig. 4). The relative intensity of this emission under air was lower for  $\text{UC}_{\text{Er}}@ \text{RB}$  ( $7.5 \times 10^{-2}$  a.u. in RB vs.  $4.3 \times 10^{-2}$  a.u. in  $\text{UC}_{\text{Er}}@ \text{RB}$ ; Fig. 4). This result is attributed to a lower generation of singlet oxygen by triplet–triplet energy transfer from  $^3\text{RB}$  on the surface of the UCNP as compared to RB in solution. Consequently, if the final purpose of the UCNH were to efficiently generate  $^1\text{O}_2$  (e.g., for photodynamic therapy), the decrease of  $\Phi_{\text{isc}}$  and  $k_{\text{q}}(\text{O}_2)$  will dramatically influence the performance of the UCNH.

### Photophysics of $\text{UC}_{\text{Er}}$ in the UCNH

Upon NIR excitation at 980 nm,  $\text{UC}_{\text{Er}}$  transfers energy to RB in  $\text{UC}_{\text{Er}}@ \text{RB}$ . Note that high chromophore absorption (despite low concentrations of UCNP) can produce secondary inner-filter effects or/and emission self-absorption that modify the shape of the emission spectrum. It is convenient to prepare diluted dispersions. Fig. 5a shows the emission spectrum of  $\text{UC}_{\text{Er}}$  and  $\text{UC}_{\text{Er}}@ \text{RB}$  at 1 mg  $\text{mL}^{-1}$  and at 5 mg  $\text{mL}^{-1}$  in which the inner-filter effect for  $\text{UC}_{\text{Er}}@ \text{RB}$  can be appreciated.

UC intensity and lifetimes were not affected by the gas atmosphere ( $\text{N}_2$  or air). As previously reported, in the UCNH, the relative intensity of the UCNP emission affected by RB

absorption (520–540 nm) decreased slightly as compared to the  $\text{UC}_{\text{Er}}$  emission (Fig. 5a), and a new emission centered at 584 nm appeared. This new band can be attributed to the sensitized emission of RB from the  $\text{Er}^{3+}$  of the UCNP, since it presents a lifetime in the order of the UC emissions of the  $\text{Er}^{3+}$  (51  $\mu\text{s}$ ; Table 2) in comparison to the conventional fluorescence of RB by direct excitation (1.5 ns). Note that the broad-emission tail of RB emission overlaps with the  $\text{Er}^{3+}$  emission at 655 nm (therefore, the  $\text{Er}^{3+}$  emission intensity increased in Fig. 5a).

Likewise, the presence of RB in the UCNH produced a slight reduction in the lifetime of the bands affected by RB absorption with respect to the precursor  $\text{UC}_{\text{Er}}$  (Table 2 and Fig. S10†). Although the presence of the dye on the surface of the UCNP did not seem to greatly affect either the relative intensities of the  $\text{Er}^{3+}$  UC emissions or its deactivation kinetics, it did affect the overall performance of the UC process. The presence of the dye reduced ca. 50% of the upconversion quantum yield (UCQY) of the UCNH with respect to the  $\text{UC}_{\text{Er}}$  (Table 2 and Fig. 5b). This is an expected result because more non-radiative deactivation phenomena will be possible by adding more electronic states to the system (with RB).

The  $^3\text{RB}$  generation sensitized by UC emissions was not observed by transient absorption spectroscopy at 980 nm (5 mJ per laser pulse). Likewise, an attempt was made to record the emission of  $^1\text{O}_2$  in a dispersion of UCNH bubbled with  $\text{O}_2$  for 20 minutes, but no signal could be detected. Although it has been widely reported that PS-functionalized UCNP are capable of generating ROS,<sup>44,70–74</sup> the sensitized formation of  $^3\text{RB}$  and  $^1\text{O}_2$  could not be spectroscopically observed under our experimental conditions, probably because the instrumentation is not sensible enough to detect these species for our system.



**Fig. 5** (a) 841 nm-normalized corrected UC emission spectra of  $\text{UC}_{\text{Er}}$  and  $\text{UC}_{\text{Er}}@ \text{RB}$  dispersions at different concentrations ( $\lambda_{\text{exc}} = 980 \text{ nm}$ ;  $I = 2.1 \text{ W cm}^{-2}$ ). (b) Power density dependency of absolute UCQY for  $\text{UC}_{\text{Er}}$  and  $\text{UC}_{\text{Er}}@ \text{RB}$  dispersions in DMF (5 mg  $\text{mL}^{-1}$ ).

**Table 2** UC emission properties of  $\text{UC}_{\text{Er}}$  and  $\text{UC}_{\text{Er}}@ \text{RB}$  in DMF under an  $\text{N}_2$  atmosphere ( $\lambda_{\text{exc}} = 980 \text{ nm}$ ). Kinetics fitting parameters are in Table S4†

Sample	$\tau_{525} \pm \text{SD}^a$ ( $\mu\text{s}$ )	$\tau_{540} \pm \text{SD}^a$ ( $\mu\text{s}$ )	$\tau_{600} \pm \text{SD}^a$ ( $\mu\text{s}$ )	$\tau_{655} \pm \text{SD}^a$ ( $\mu\text{s}$ )	$\text{UCQY}_{\text{sat}} \pm \text{SD}^a$ <sup>b</sup>
$\text{UC}_{\text{Er}}$	$85.9 \pm 0.1$	$85.7 \pm 0.1$	—	$205 \pm 9$	$0.29 \pm 0.1$
$\text{UC}_{\text{Er}}@ \text{RB}$	$59.5 \pm 0.1$	$59.3 \pm 0.1$	$51.3 \pm 0.1$	$202 \pm 5$	$0.14 \pm 0.1$

<sup>a</sup> SD: standard deviation. <sup>b</sup> UCQY in a saturation regime at  $2.24 \text{ kW cm}^{-2}$ , 5 mg  $\text{mL}^{-1}$  dispersion.



## Conclusions

In summary, the results here described shed light on unresolved questions when functionalizing an UCNP with a xanthenic dye, such as RB. The photophysics of RB can be drastically affected by the aggregation and interaction with the UCNP surface and the presence of photoactive lanthanide cations ( $\text{Yb}^{3+}$ ,  $\text{Er}^{3+}$ ) doping the UCNP matrix.

The low functionalization degree and RB aggregation in  $\text{UC}_{\text{Er}}@\text{RB}$  are attributed to the high concentration of RB in DMF used for functionalization. Equally important, the dynamics of RB excited states were roundly changed:  $\Phi_{\text{F}}$  and  $\Phi_{\text{isc}}$  decreased (specially the  $\Phi_{\text{F}}$ ) and both  $^1\text{RB}$  and  $^3\text{RB}$  excited states were deactivated by means of energy transfer processes from the dye to the photoactive lanthanides in the UCNPs (lower emission intensity and shorter fluorescence and phosphorescence lifetimes). As far as we know, this is the first experimental demonstration of the equal contribution of  $^1\text{RB}$  and  $^3\text{RB}$  to the antenna effect from RB to  $\text{Yb}^{3+}$  and  $\text{Er}^{3+}$ , which results in NIR-II emissions. Indeed, as previously reported for similar UCNHs, the UC emission spectra showed little influence on the intensity ratio of the  $\text{Ln}^{3+}$  emission bands for the nanohybrid (when avoiding the secondary inner filter effect), and a new sensitized long-lived emission from RB was detected due to a resonant energy transfer from  $\text{Er}^{3+}$  to  $^1\text{RB}$ . Moreover, the absolute external UCQY of the system decreased to half as compared to that of the pristine UCNP. Therefore, rather than a synergistic or additive effect, in this UCNH, we observed an antagonistic effect which limits its potential application as a bioimaging or  $^1\text{O}_2$  generation agent.

All in all, it was demonstrated that the dye photophysics in solution cannot be taken for granted when functionalizing UCNPs, and every case should be studied in advance to ensure a synergistic rather than an antagonistic effect. This knowledge is of utmost importance to design efficient functional UCNHs. In the case of designing bioimaging probes, a reduction in the dye  $\Phi_{\text{F}}$  will be an additional limitation to the low UCQY of the UCNP. Similarly, as shown here for the  $\text{UC}_{\text{Er}}@\text{RB}$  nanohybrid, if the aim is to generate  $^1\text{O}_2$ , the reduction in the dye  $\Phi_{\text{isc}}$  together with the slower diffusion of the colloid will negatively affect the  $^1\text{O}_2$  quantum yield. In this example, the doping of the UCNP with  $\text{Gd}^{3+}$  may be a plausible and rational solution. In any case, the effects of  $\text{Gd}^{3+}$  doping, UCNP size, dye loading, and concentration used for the functionalization process, the distance between  $\text{Ln}^{3+}$  and dyes, and chromophores with different ratios of singlet/triplet need to be studied in the future to design UCNHs.

## Author contributions

Juan Ferrera-González: investigation, methodology, data curation, visualization, and writing – original draft; María González-Béjar: conceptualization, supervision, and writing – review & editing; Julia Pérez-Prieto: conceptualization, supervision, and writing – review & editing.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This research was funded by MINECO (grant number PID2020-115710GB-I00); Agencia Estatal de Investigación-AEI (grant number MMCIU Unit of Excellence “Maria de Maeztu” CEX2019-000919-M); Ministerio de Educación, Cultura y Deporte (FPU grant J.F.-G.); and Generalitat Valenciana (grant numbers CIPROM/2022/57 and IDIFEDER/2018/064), all of them partially co-financed with FEDER funds. This study forms part of the Advanced Materials programme (MFA/2022/051) and was supported by MICIN with funding from the European Union NextGenerationEU (PRTR-C17.I1) and by Generalitat Valenciana. TEM and ICP-MS were performed in Servicio Central de Soporte a la Investigación Experimental (SCSIE, University of Valencia).

## References

- 1 F. Auzel, *Chem. Rev.*, 2004, **104**, 139–173.
- 2 G. Tessitore, G. A. Mandl, M. G. Brik, W. Park and J. A. Capobianco, *Nanoscale*, 2019, **11**, 12015–12029.
- 3 X. Li, F. Zhang and D. Zhao, *Chem. Soc. Rev.*, 2015, **44**, 1346–1378.
- 4 M. R. Hamblin, *Dalton Trans.*, 2018, **47**, 8571–8580.
- 5 M. González-Béjar, L. Francés-Soriano and J. Pérez-Prieto, *Front. Bioeng. Biotechnol.*, 2016, **4**, 47.
- 6 X. Zhu, J. Zhang, J. Liu and Y. Zhang, *Adv. Sci.*, 2019, **6**, 1901358.
- 7 B. Chen and F. Wang, *Trends Chem.*, 2020, **2**, 427–439.
- 8 W. Xu, X. Chen and H. Song, *Nano Today*, 2017, **17**, 54–78.
- 9 W. Xu, H. Liu, D. Zhou, X. Chen, N. Ding, H. Song and H. Ågren, *Nano Today*, 2020, **33**, 100892.
- 10 E. Andresen, U. Resch-Genger and M. Schäferling, *Langmuir*, 2019, **35**, 5093–5113.
- 11 F. Pini, L. Francés-Soriano, V. Andriago, M. M. Natile and N. Hildebrandt, *ACS Nano*, 2023, **17**, 4971–4984.
- 12 L. Francés-Soriano, N. Estebanez, J. Pérez-Prieto and N. Hildebrandt, *Adv. Funct. Mater.*, 2022, **32**, 2201541.
- 13 J. Ferrera-González, M. González-Béjar and J. Pérez-Prieto, in *Dyes and Photoactive Molecules in Microporous Systems. Structure and Bonding*, ed. F. López Arbeloa, Springer, Cham, 2020, pp. 371–396.
- 14 X. Wang, R. R. Valiev, T. Y. Ohulchanskyy, H. Ågren, C. Yang and G. Chen, *Chem. Soc. Rev.*, 2017, **46**, 4150–4167.
- 15 Y. Liu, X. Meng and W. Bu, *Coord. Chem. Rev.*, 2019, **379**, 82–98.
- 16 A. Zhou, Y. Wei, B. Wu, Q. Chen and D. Xing, *Mol. Pharm.*, 2012, **9**, 1580–1589.
- 17 Q. Yuan, Y. Wu, J. Wang, D. Lu, Z. Zhao, T. Liu, X. Zhang and W. Tan, *Angew. Chem., Int. Ed.*, 2013, **52**, 13965–13969.



- 18 M. González-Béjar, M. Liras, L. Francés-Soriano, V. Voliani, V. Herranz-Pérez, M. Duran-Moreno, J. M. Garcia-Verdugo, E. I. Alarcon, J. C. Scaiano and J. Pérez-Prieto, *J. Mater. Chem. B*, 2014, **2**, 4554–4563.
- 19 K. Liu, X. Liu, Q. Zeng, Y. Zhang, L. Tu, T. Liu, X. Kong, Y. Wang, F. Cao, S. A. G. G. Lambrechts, M. C. G. G. Aalders and H. Zhang, *ACS Nano*, 2012, **6**, 4054–4062.
- 20 F. Chen, S. Zhang, W. Bu, Y. Chen, Q. Xiao, J. Liu, H. Xing, L. Zhou, W. Peng and J. Shi, *Chem. – Eur. J.*, 2012, **18**, 7082–7090.
- 21 X. Yang, Q. Xiao, C. Niu, N. Jin, J. Ouyang, X. Xiao and D. He, *J. Mater. Chem. B*, 2013, **1**, 2757–2763.
- 22 Y. Il Park, H. M. Kim, J. H. Kim, K. C. Moon, B. Yoo, K. T. Lee, N. Lee, Y. Choi, W. Park, D. Ling, K. Na, W. K. Moon, S. H. Choi, H. S. Park, S.-Y. Yoon, Y. D. Suh, S. H. Lee and T. Hyeon, *Adv. Mater.*, 2012, **24**, 5755–5761.
- 23 P. Zhang, W. Steelant, M. Kumar and M. Scholfield, *J. Am. Chem. Soc.*, 2007, **129**, 4526–4527.
- 24 A. M. Kotulska, A. Pilch-Wróbel, S. Lahtinen, T. Soukka and A. Bednarkiewicz, *Light: Sci. Appl.*, 2022, **11**, 1–14.
- 25 A. Pilch-Wróbel, A. M. Kotulska, S. Lahtinen, T. Soukka and A. Bednarkiewicz, *Small*, 2022, **18**, 2200464.
- 26 S. Melle, O. G. Calderón, M. Laurenti, D. Mendez-Gonzalez, A. Egatz-Gómez, E. López-Cabarcos, E. Cabrera-Granado, E. Díaz and J. Rubio-Retama, *J. Phys. Chem. C*, 2018, **122**, 18751–18758.
- 27 R. Marin, L. Labrador-Paéz, A. Skripka, P. Haro-González, A. Benayas, P. Canton, D. Jaque and F. Vetrone, *ACS Photonics*, 2018, **5**, 2261–2270.
- 28 O. Dukhno, F. Przybilla, M. Collot, A. Klymchenko, V. Pivovarenko, M. Buchner, V. Muhr, T. Hirsch and Y. Mély, *Nanoscale*, 2017, **9**, 11994–12004.
- 29 F. Pini, L. Francés-Soriano, N. Peruffo, A. Barbon, N. Hildebrandt and M. M. Natile, *ACS Appl. Mater. Interfaces*, 2022, **14**, 11883–11894.
- 30 S. Bhuckory, S. Lahtinen, N. Höysniemi, J. Guo, X. Qiu, T. Soukka and N. Hildebrandt, *Nano Lett.*, 2023, **23**, 2253–2261.
- 31 D. J. Garfield, N. J. Borys, S. M. Hamed, N. A. Torquato, C. A. Tajon, B. Tian, B. Shevitski, E. S. Barnard, Y. D. Suh, S. Aloni, J. B. Neaton, E. M. Chan, B. E. Cohen and P. J. Schuck, *Nat. Photonics*, 2018, **12**, 402–407.
- 32 S. Han, R. Deng, Q. Gu, L. Ni, U. Huynh, J. Zhang, Z. Yi, B. Zhao, H. Tamura, A. Pershin, H. Xu, Z. Huang, S. Ahmad, M. Abdi-Jalebi, A. Sadhanala, M. L. Tang, A. Bakulin, D. Beljonne, X. Liu and A. Rao, *Nature*, 2020, **587**, 594–599.
- 33 S. Han, Z. Yi, J. Zhang, Q. Gu, L. Liang, X. Qin, J. Xu, Y. Wu, H. Xu, A. Rao and X. Liu, *Nat. Commun.*, 2021, **12**, 1–9.
- 34 P. Zhang, J. Ke, D. Tu, J. Li, Y. Pei, L. Wang, X. Shang, T. Guan, S. Lu, Z. Chen and X. Chen, *Angew. Chem., Int. Ed.*, 2022, **61**, e202112125.
- 35 X. Wang, X. Wang, G. V. Baryshnikov, R. R. Valiev, R. Fan, S. Lu, H. Ågren and G. Chen, *Chem. Eng. J.*, 2021, **426**, 131282.
- 36 K. R. Gopidas and P. V. Kamat, *J. Phys. Chem.*, 1989, **93**, 6428–6433.
- 37 C. Nasr, D. Liu, S. Hotchandani and P. V. Kamat, *J. Phys. Chem.*, 1996, **100**, 11054–11061.
- 38 I.-I. S. Lim, F. Goroleski, D. Mott, N. Kariuki, W. Ip, J. Luo and C.-J. Zhong, *J. Phys. Chem. B*, 2006, **110**, 6673–6682.
- 39 V. Muhr, C. Würth, M. Kraft, M. Buchner, A. J. Baeumner, U. Resch-Genger and T. Hirsch, *Anal. Chem.*, 2017, **89**, 4868–4874.
- 40 L. Ludvíková, P. Friš, D. Heger, P. Šebej, J. Wirz and P. Klán, *Phys. Chem. Chem. Phys.*, 2016, **18**, 16266–16273.
- 41 M. C. DeRosa and R. J. Crutchley, *Coord. Chem. Rev.*, 2002, **233–234**, 351–371.
- 42 W. Liu, Y. Zhang, W. You, J. Su, S. Yu, T. Dai, Y. Huang, X. Chen, X. Song and Z. Chen, *Nanoscale*, 2020, **12**, 13948–13957.
- 43 F. Jin, J. Qi, D. Liu, Y. You, G. Shu, Y. Du, J. Wang, X. Xu, X. Ying, J. Ji and Y. Du, *J. Controlled Release*, 2021, **337**, 90–104.
- 44 X. Chen, Y. Zhang, X. Zhang, Z. Zhang and Y. Zhang, *Microchim. Acta*, 2021, **188**, 1–10.
- 45 Y. Wang, K. Liu, X. Liu, K. Dohnalová, T. Gregorkiewicz, X. Kong, M. C. G. Aalders, W. J. Buma and H. Zhang, *J. Phys. Chem. Lett.*, 2011, **2**, 2083–2088.
- 46 Z. Li and Y. Zhang, *Nanotechnology*, 2008, **19**, 16–21.
- 47 A. Dong, X. Ye, J. Chen, Y. Kang, T. Gordon, J. M. Kikkawa and C. B. Murray, *J. Am. Chem. Soc.*, 2011, **133**, 998–1006.
- 48 N. J. Hestand and F. C. Spano, *Chem. Rev.*, 2018, **118**, 7069–7163.
- 49 B. Mendes, S. Kassumeh, A. Aguirre-Soto, Q. Pei, B. Heyne and I. E. Kochevar, *Photochem. Photobiol.*, 2021, **97**, 718–726.
- 50 M. E. Daraio and E. San Román, *Helv. Chim. Acta*, 2001, **84**, 2601–2614.
- 51 D. Xu and D. C. Neckers, *J. Photochem. Photobiol., A*, 1987, **40**, 361–370.
- 52 E. Alarcón, A. M. Edwards, A. Aspée, C. D. Borsarelli and E. A. Lissi, *Photochem. Photobiol. Sci.*, 2009, **8**, 933–943.
- 53 H. B. Rodríguez, M. G. Lagorio and E. S. Román, *Photochem. Photobiol. Sci.*, 2004, **3**, 674–680.
- 54 P. Montes-Navajas, A. Corma and H. Garcia, *ChemPhysChem*, 2008, **9**, 713–720.
- 55 P. Montes-Navajas, M. González-Béjar, J. C. Scaiano and H. García, *Photochem. Photobiol. Sci.*, 2009, **8**, 1743–1747.
- 56 O. Valdes-Aguilera and D. C. Neckers, *J. Photochem. Photobiol., A*, 1989, **47**, 213–222.
- 57 O. Valdes-Aguilera and D. C. Neckers, *J. Phys. Chem.*, 2002, **92**, 4286–4289.
- 58 M. B. E. Turbay, V. Rey, N. M. Argañaraz, F. E. Morán Vieyra, A. Aspée, E. A. Lissi and C. D. Borsarelli, *J. Photochem. Photobiol., B*, 2014, **141**, 275–282.
- 59 Y. Litman, M. G. Voss, H. B. Rodríguez and E. S. Román, *J. Phys. Chem. A*, 2014, **118**, 10531–10537.
- 60 P. V. Kamat and W. E. Ford, *Chem. Phys. Lett.*, 1987, **135**, 421–426.





- 61 W. Ren, S. Wen, S. A. Tawfik, Q. P. Su, G. Lin, L. A. Ju, M. J. Ford, H. Ghodke, A. M. Van Oijen and D. Jin, *Chem. Sci.*, 2018, **9**, 4352–4358.
- 62 H. Na, K. Woo, K. Lim and H. S. Jang, *Nanoscale*, 2013, **5**, 4242–4251.
- 63 S. Lahtinen, A. Lyytikäinen, H. Pääkkilä, E. Hömppi, N. Perälä, M. Lastusaari and T. Soukka, *J. Phys. Chem. C*, 2017, **121**, 656–665.
- 64 W. E. Ford and P. V. Kamat, *J. Phys. Chem.*, 1989, **93**, 6423–6428.
- 65 G. A. Hebbink, L. Grave, L. A. Woldering, D. N. Reinhoudt and F. C. J. M. Van Veggel, *J. Phys. Chem. A*, 2003, **107**, 2483–2491.
- 66 S. L. Murov, I. Carmichael and G. L. Hug, in *Handbook of Photochemistry*, Marcel Dekker, INC., New York, 2nd edn, 1993, pp. 1–53.
- 67 H. C. Junqueira, D. Severino, L. G. Dias, M. S. Gugliotti and M. S. Baptista, *Phys. Chem. Chem. Phys.*, 2002, **4**, 2320–2328.
- 68 F. Stracke, M. Heupel and E. Thiel, *J. Photochem. Photobiol. A*, 1999, **126**, 51–58.
- 69 C. A. Parker and C. G. Hatchard, *Trans. Faraday Soc.*, 1961, **57**, 1894–1904.
- 70 C. Wang, L. Cheng and Z. Liu, *Theranostics*, 2013, **3**, 317–330.
- 71 N. M. Idris, M. K. Gnanasammandhan, J. Zhang, P. C. Ho, R. Mahendran and Y. Zhang, *Nat. Med.*, 2012, **18**, 1580–1585.
- 72 C. Wang, H. Tao, L. Cheng and Z. Liu, *Biomaterials*, 2011, **32**, 6145–6154.
- 73 D. Zhang, L. Wen, R. Huang, H. Wang, X. Hu and D. Xing, *Biomaterials*, 2018, **153**, 14–26.
- 74 Y. Liu, X. Meng and W. Bu, *Coord. Chem. Rev.*, 2019, **379**, 82–98.
- 75 S. L. Murov, I. Carmichael and G. L. Hug, *Handbook of Photochemistry*, Marcel Dekker, INC., New York, 2nd edn, 1993.

