

Cite this: *Energy Adv.*, 2023,
2, 465

A comprehensive review of cathode materials for Na–air batteries

Pengcheng Mao,^a Hamidreza Arandiyani,^{id *bc} Sajjad S. Mofarah,^{id d}
Pramod Koshy,^{id d} Cristina Pozo-Gonzalo,^{id e} Runguo Zheng,^a Zhiyuan Wang,^{id a}
Yuan Wang,^{id *e} Suresh K. Bhargava,^{id c} Hongyu Sun,^{id *a} Zongping Shao^f and
Yanguo Liu^{*a}

In recent years, rechargeable sodium–air batteries have attracted extensive attention and shown rapid development for use in the field of electrochemical energy storage owing to low costs, abundance of the precursor resources, high theoretical specific capacity, and high energy density, all of which have contributed to making them one of the most promising alternatives to lithium-ion batteries. Despite the numerous advantages, Na–air batteries also face certain challenges, such as poor charge–discharge reversibility at the cathode, formation of sodium dendrites at the anode, and low catalytic activity for oxygen reduction/evolution reactions. Thus, designing efficient and stable air cathode materials is significant for the development and practical application of Na–air batteries. Therefore, this paper aims to review the advances related to the development of air cathodes in Na–air batteries in the last decade. Here, research on the secondary Na–air batteries are briefly summarized and divided into two categories based on their electrolyte composition: organic Na–air batteries and hybrid Na–air batteries. The air cathode materials are reviewed and categorised based on the material type into the following: carbon materials, transition metals and metal oxides, noble metals, perovskites and spinel oxides, metal–organic frameworks and their derivatives, pyrochlore oxides, and other cathode materials. Furthermore, work in previous studies applying *in situ* spectroelectrochemical techniques, including Infrared spectroscopy, electron spin resonance, UV/Vis spectroscopy, and Raman spectroscopy, to develop the structure–performance correlations and redox reaction mechanisms of Na–air batteries are summarised. Finally, the challenges faced by Na–air batteries and the prospect of future work are discussed in the conclusions. This review is thus expected to provide a comprehensive understanding of the trends and issues related to the development of Na–air batteries for practical industrial applications.

Received 6th December 2022,
Accepted 21st February 2023

DOI: 10.1039/d2ya00340f

rsc.li/energy-advances

1. Introduction

Shortage of energy supply and increased environmental pollution are major issues currently, posing challenges to the sustainable development of human society.^{1–4} The development of green and efficient new energy resources, improvement

of energy distribution mechanisms, and rectification of energy shortages have become the main global priorities.^{1,3} Therefore, lithium-ion batteries (LIBs) have been gaining increasing attention due to their excellent stability, high cycle efficiency, and low electrode potential.^{5–10} However, their low energy (<500 W h kg⁻¹) and power densities have limited their large-scale application (Table 1).¹¹ Even though researchers continue to rationalize the processes to optimize the materials and structures, the limited energy density and safety concerns related to the Li-ion batteries have prevented them from reaching the levels required to meet current energy demands.¹² Therefore, it is imperative that 'green' chemical power be developed with high specific energy and energy density in order to replace existing commercial LIBs. Recently, there has been a great deal of interest in metal–air batteries as an energy storage device due to their high theoretical energy density. Metal–air batteries are secondary batteries in which metal serves as the anode. Air or oxygen undergoes a reduction reaction at the

^a School of Resources and Materials, Northeastern University at Qinhuangdao, Qinhuangdao 066004, P. R. China. E-mail: hyltsun@gmail.com, lyg@neuq.edu.cn^b Laboratory of Advanced Catalysis for Sustainability, School of Chemistry, University of Sydney, Sydney, NSW 2006, Australia. E-mail: hamid.arandiyani@sydney.edu.au^c Centre for Applied Materials and Industrial Chemistry (CAMIC), School of Science, RMIT University, Melbourne, VIC 3000, Australia^d School of Materials Science and Engineering, UNSW Sydney, Sydney, NSW 2052, Australia^e Institute for Frontier Materials, Deakin University, Melbourne, VIC 3125, Australia. E-mail: wang@deakin.edu.au^f WA School of Mines: Minerals, Energy and Chemical Engineering, Curtin University, Perth, WA 6845, Australia

cathode to generate current. The most significant benefit of air batteries is that the positive active material is oxygen from the air. This is inexhaustible and does not need to be stored inside the battery, thus providing a high energy density. In the future, this technology may be used as an alternative to lithium-ion batteries since it serves as a power battery with high specific energy.^{13–18} Table 1 compares the characteristics of LIBs, the lithium–air batteries (LABs), the Na-ion batteries (NIBs) and the Na–air batteries (SABs). It can be clearly seen that the metal–air batteries exhibit higher specific capacity and energy density compared to the metal–ion batteries, which is favorable to promote the industrial application of metal–air batteries.

LABs were first reported in 1996 and have attracted widespread attention since then owing to their extremely high specific capacity and outstanding theoretical energy density (3500 W h kg^{-1}).¹⁹ However, the high overpotential during the charging/discharging process makes the round-trip efficiency relatively low, resulting in relatively poor reversible performance and cycle stability.^{20–22} Considering the shortage of metal lithium resources and the similar physical and chemical properties of metal sodium and lithium,^{22–24} the replacement of metal lithium with metal sodium has become a hot spot in battery research and SABs as a future energy storage device have also attracted the interest of many researchers.^{25–29} The emergence of SABs is an important step forward in the research on



Pengcheng Mao

Pengcheng Mao is currently a Master's student under the supervision of Prof. Yanguo Liu at the Northeastern University. He has been studying the applications of conductive polymer, including metal–organic frameworks, in energy storage and conversion. Meanwhile, he is interested in the influence of interface interaction (homogeneous interface, heterogeneous interface) on ions and electron transport, devoting himself to developing batteries with high energy density and ultra-fast charging ability.



Hamidreza Arandiyani

Hamidreza Arandiyani received his PhD from Tsinghua University in 2014. He was awarded a Vice-Chancellor's Research Fellowship from UNSW Sydney in 2015. He was a University of Sydney Senior Fellowship in the School of Chemistry in 2018. Currently, he is a Senior Research Fellow in the Applied Chemistry & Environmental Science at RMIT University, Melbourne, expanding his work on functional battery materials. His research interests lie in heterogeneous catalysis for environmental remediation and energy applications.



Sajjad S. Mofarah

Sajjad S. Mofarah obtained his PhD in Materials Science and Engineering, UNSW Sydney, in 2020, with a focus on electrochemistry-based synthesis and characterisation of 2D metal oxides, heterostructures, and coordination polymers for energy storage and catalysis applications. He was appointed as a Research Associate at SMaRT Centre at UNSW in April 2020 to work on cyclic reprocessing of battery materials and recovery of wastes

into functional nanostructures for electrocatalysis and capacitance applications. Upon being appointed as Senior Research Associate at the NEMCAT group, UNSW Sydney, and Chief Scientist at Vecor Technologies Pty. Ltd. in 2022, he started working on research and development of cathodic materials for lithium and sodium rechargeable batteries. Among his research interests are fabrication, advanced characterization, and thermodynamic analyses of defective layered oxides and perovskites for energy storage applications.



Pramod Koshy

Pramod Koshy received his PhD in Materials Science and Engineering, UNSW Sydney in 2009. He has worked as a researcher in the same organization after that and has received continuous funding from industries and the Australian Research Council. He is currently employed as an Associate Professor and co-leads the NEMCAT research group at UNSW Sydney. His primary research has focused on the development of materials and technologies in waste resource transformation, nano-biomaterials, and catalytic material development for air and water purification. He has also supervised over 50 higher students and over 90 Honours students to completion.



LIBs, LABs and SIBs. Replacing lithium with sodium, which is more abundant on earth, removes a bottleneck in the resource supply chain and results in lower production costs. Using oxygen from air instead of solid redox-active materials significantly increases the battery's specific capacity and energy density. In 2011, Avshalomov *et al.*³⁰ assembled and operated the sodium–air battery with liquid–sodium anode at 105 °C. The successful operation of the high-temperature Na–air battery shows that it is feasible for this battery to replace the Li–air battery. However, the assembly and operation of high-

temperature Na–air batteries are not practical for commercial use. Later, Fu *et al.*²⁸ developed a novel room-temperature sodium–air battery with an air electrode exhibiting a high specific capacity of 1884 mA h g⁻¹ at a current density of 1/10C. Due to the very high activity of sodium metal, the SABs had to be operated in an organic electrolyte and a dry, pure oxygen environment. During the SAB discharge process, Na⁺ is released from the sodium metal anode by an oxidation reaction, and Na⁺ combines with superoxide anion, O₂^{•-}, at the cathode to form the discharge product sodium superoxide (NaO₂); the reverse



Cristina Pozo-Gonzalo

Cristina Pozo-Gonzalo attained her degree and honours at the University of Zaragoza (Spain). After graduating, she received her PhD degree in Chemistry from the University of Manchester (United Kingdom) under the supervision of Prof. Peter J. Skabara on the electrochemical synthesis of Conducting Polymers. After moving to Australia, she worked with Prof. Alan Bond at Monash University, and in 2012 she joined Deakin University, where she has been working in reversible metal–air batteries with advanced electrolytes, ionic liquids funded by ARC Centre of Excellence for Electromaterials Science (ACES). Her research interests include metal–air batteries ionic liquids, circular economy, conducting polymers, and critical metal extraction and recovery. In her research career, she has published 95 publications, including 4 patents and 3 book chapters, and managed 33 projects as chief investigator.

Cristina Pozo-Gonzalo attained her degree and honours at the University of Zaragoza (Spain). After graduating, she received her PhD degree in Chemistry from the University of Manchester (United Kingdom) under the supervision of Prof. Peter J. Skabara on the electrochemical synthesis of Conducting Polymers. After moving to Australia, she worked with Prof. Alan Bond at Monash University, and in 2012 she



Yuan Wang

Yuan Wang (Helena) received her PhD degree from the School of Chemical Engineering, The University of New South Wales (UNSW) Sydney Australia in 2018. She was appointed as a Research Assistant at the National Research Center for Geoanalysis, Chinese Academy of Geological Science in 2013. She was a Postdoctoral Research Associate in the School of Chemistry, UNSW Sydney and a Research Fellow in the Applied Chemistry & Environmental Science at RMIT University, Melbourne. Current, she is an Alfred Deakin Research Fellow in the Institute for Frontier Materials (IFM) at Deakin University, Melbourne. Her research interests focus on developing and characterising nanoporous materials for metal–air batteries and electrocatalytic applications.

Yuan Wang (Helena) received her PhD degree from the School of Chemical Engineering, The University of New South Wales (UNSW) Sydney Australia in 2018. She was appointed as a Research Assistant at the National Research Center for Geoanalysis, Chinese Academy of Geological Science in 2013. She was a Postdoctoral Research Associate in the School of Chem-



Suresh K. Bhargava

Dist. Prof. Suresh Bhargava is a world-renowned interdisciplinary scientist with decades of leadership in academia and industry. With over 600 highly cited publications including 2 books and 16 book chapters, 12 patents (6 transferred to industry) with >23 000 citations. A recipient of many awards, Prof. Bhargava's academic excellence and remarkable aptitude in integrating fundamental science with engineering set him apart as a global leader of translational research. The contributions of Prof. Suresh Bhargava exceed far beyond academic knowledge into the realm of new discoveries, invention of new technologies and successful implementation of industrial processes. He is a fellow of seven academies around the world including ATSE, AAS and TWAS.

Dist. Prof. Suresh Bhargava is a world-renowned interdisciplinary scientist with decades of leadership in academia and industry. With over 600 highly cited publications including 2 books and 16 book chapters, 12 patents (6 transferred to industry) with >23 000 citations. A recipient of many awards, Prof. Bhargava's academic excellence and remarkable aptitude in integrating fundamental science with engineering set him apart



Hongyu Sun

Hongyu Sun received his PhD degree from the State Key Laboratory of Metastable Materials Science and Technology, Yanshan University in 2010. He then spent 2 years as a Postdoctoral Research Fellow in the Department of Materials Science and Engineering, Tsinghua University under the direction of Prof. Jing Zhu. He then joined the Beijing National Centre for Electron Microscopy, Tsinghua University. In 2015, he moved to the Technical University of Denmark as a Postdoctoral Research Fellow. His research interests include controllable synthesis of nanostructures for applications in energy storage and conversion (lithium/sodium-ion batteries, electrolysis), liquid cell transmission electron microscopy, and microfabrication.

Hongyu Sun received his PhD degree from the State Key Laboratory of Metastable Materials Science and Technology, Yanshan University in 2010. He then spent 2 years as a Postdoctoral Research Fellow in the Department of Materials Science and Engineering, Tsinghua University under the direction of Prof. Jing Zhu. He then joined the Beijing National Centre for Electron Microscopy, Tsinghua University. In 2015, he




occurs during the subsequent charging process.^{11,31,32} Based on the discharge product being sodium superoxide (NaO_2), the theoretical energy density of SABs is 1108 W h kg^{-1} , which is very attractive in comparison to the limited energy density of LIBs.³³ Interestingly, the formation of NaO_2 during the discharge process of SABs competes with the precipitation of sodium peroxide (Na_2O_2).³⁴ Although Na_2O_2 is thermodynamically stable compared to NaO_2 , Na_2O_2 involves a two-electron transfer process, which is kinetically slower compared to the single-electron transfer of NaO_2 .^{33,34} Meanwhile, the SABs with NaO_2 as the discharge product have a lower overpotential compared to those with Na_2O_2 as the discharge product, thereby favouring both higher energy efficiency and improved cycle stability.^{11,35,36} Therefore, to realize long-cycle stability and low overpotential for Na–O₂ batteries, it is essential to conduct an in-depth study on the chemical composition of air cathodes and electrolytes in order to reduce the side reactions.

Despite their desirable high energy density, research on SABs is still in its infancy compared to the current state-of-the-art research on sodium-ion batteries. Many scientific issues still need to be addressed before SABs can be applied practically.^{37,38} These include (i) factors, such as types, physicochemical properties, and microstructures of electrodes, and their effects on the composition and morphology of sodium–air battery discharge products, and (ii) careful selection and design of electrolyte compositions with excellent chemical and electrochemical stability along with appropriate electrochemical windows that prevent superoxide radical formation and associated side reactions and the sudden death of the batteries. In addition, the protection of the sodium anode from trace water in the electrolyte and the suppression of the formation of sodium dendrites also play an important role in ensuring the high performance of sodium–air batteries. This review will comprehensively summarize the research progress with regard

to cathode materials for sodium–air batteries. The first part will discuss the basic theory and chemical reaction processes of air battery cathodes, while the next section will summarize the types and designs of air cathodes consisting of different materials, including carbon-based, transition metals and metal oxides, noble metals, chalcogenides and spinels, metal–organic frameworks and their derivatives, and other materials. This will be followed by a summary of the *in situ* spectroelectrochemical techniques employed in the research on sodium–air batteries, which are beneficial to promote the rapid development of sodium–air batteries. Finally, the strategies to improve the performance of sodium–air batteries and encourage the practical application of these devices are summarized, along with prospects for future development.

2. Metal–air batteries: theory and basic principle

The discharge/charge reaction mechanisms of metal–air batteries differ from that of conventional lithium-ion or sodium-ion batteries in that the energy density depends primarily on the type of discharge products. The cathode of metal–air batteries only provides the location for nucleation and growth of the discharge products during the discharge process. In various metal–air battery systems, the difference in their energy densities depends mainly on the volume and weight of the discharge products and the redox potentials, regardless of the battery structure. Due to the physical and chemical properties of metallic Li and Na, Na–air and Li–air batteries are very similar in terms of reaction mechanisms and battery configurations (Table 1). Taking the organic Li–air batteries as an example, the lithium metal anode is oxidized to lithium ions during the discharge process and the O₂ at the cathode diffuses into the porous electrode, dissolves in the electrolyte, and is

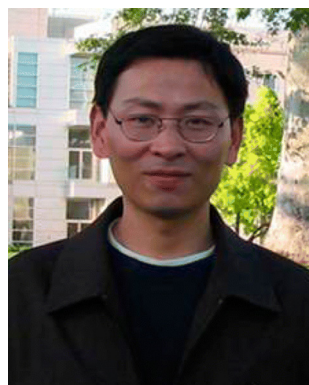

Zongping Shao

Zongping Shao is a Professor of Chemical Engineering at Curtin University, Australia and Nanjing Tech University, China. He obtained his PhD from Dalian Institute of Chemical Physics, China in 2000. He worked as a Visiting Scholar at the Institut de Recherches sur la Catalyse, CNRS, France and as a Postdoctoral Research Fellow at the California Institute of Technology, USA, from 2000 to 2005. His research interests include solid oxide fuel cells, lithium-ion batteries, supercapacitors, and low-temperature energy-conversion devices. He has been recognised as a Highly Cited Researcher in the Energy section by Elsevier since 2015. He has also been selected as a World Highly Cited Researcher by (Thomson Reuters) Clarivate Analytics for 2014, 2017, 2018, and 2019.



Yanguo Liu




Yanguo Liu received his PhD degree in Material Physics and Chemistry from Yanshan University in 2009. He is currently a Professor at Northeastern University. His research interests include functional nanostructures and energy science. He has published over 50 papers in peer-reviewed journals and holds 15 patents on energy storage materials.




Table 1 Comparison of the characteristics of Na–air batteries with Li–ion batteries, Li–air batteries and Na–ion batteries

| Battery | Redox reaction | Theoretical capacity/ mA h g^{-1} | Standard potential/V | Overpotential/ mV | Energy density/ W h kg^{-1} | Cycling life | Abundance of the component | Price/ $\text{\$T}^{-1}$ |
|------------------|---|--|----------------------|----------------------|---|--------------|----------------------------|-----------------------------|
| Li-ion batteries | $\text{Li}_{0.5}\text{CoO}_2 + 0.5\text{Li} \rightarrow \text{LiCoO}_2$ | 150 (LiCoO_2) | ~ 4.0 | — | ~ 500 (LiCoO_2) | > 500 | Li: 0.017 Co: 0.03 | 5000 |
| Li-air batteries | $2\text{Li} + \text{O}_2 \rightarrow \text{Li}_2\text{O}_2$ | 1168 (Li_2O_2) | 2.96 | > 1000 | ~ 3500 (Li_2O_2) | ~ 500 | Li: 0.017 | 5000 |
| Na-ion batteries | $\text{NaV}_2(\text{PO}_4)_3 + 2\text{Na} \rightarrow \text{Na}_3\text{V}_2(\text{PO}_4)_3$ | 117.6 ($\text{Na}_3\text{V}_2(\text{PO}_4)_3$) | 3.4 | — | ~ 180 ($\text{Na}_3\text{V}_2(\text{PO}_4)_3$) | 3000 | Na: 2.83 | 150 |
| Na-air batteries | $\text{Na} + \text{O}_2 \rightarrow \text{NaO}_2$ | 488 (NaO_2) | 2.27 | < 200 | ~ 1108 (NaO_2) | ~ 2000 | Na: 2.83 | 150 |

reduced during discharge. Li_2O_2 will be produced as the final discharge product and then decomposed during the charging process. This can be explained using the Lewis acid–base theory: Li^+ is a hard Lewis acid with small size and low polarizability, while O_2^- is a soft Lewis base with larger size, so LiO_2 is a “soft–hard compound”. This “soft–hard compound” is usually unstable and prone to decomposition, further resulting in formation of O_2^{2-} from O_2^- and Li_2O_2 as the final discharge product. When the battery is charged, this process is reversed. The electrochemical reactions are shown in eqn (1)–(3).






The most studied Na–air batteries are organic–electrolyte Na–air batteries and hybrid–electrolyte Na–air batteries, which differ slightly in terms of their structure (Fig. 1a and b). Fig. 1c describes the timeline related to the research and development of Na–air batteries. In the case of the organic electrolyte Na–air battery, the anode is sodium metal. The cathode is a bifunctional catalyst with a porous structure, while the separator is immersed in the organic electrolyte to prevent short-circuiting.³⁹ In early Na–air batteries, carbonate-based electrolytes were used, but the superoxide anion ($\text{O}_2^{\bullet-}$) would

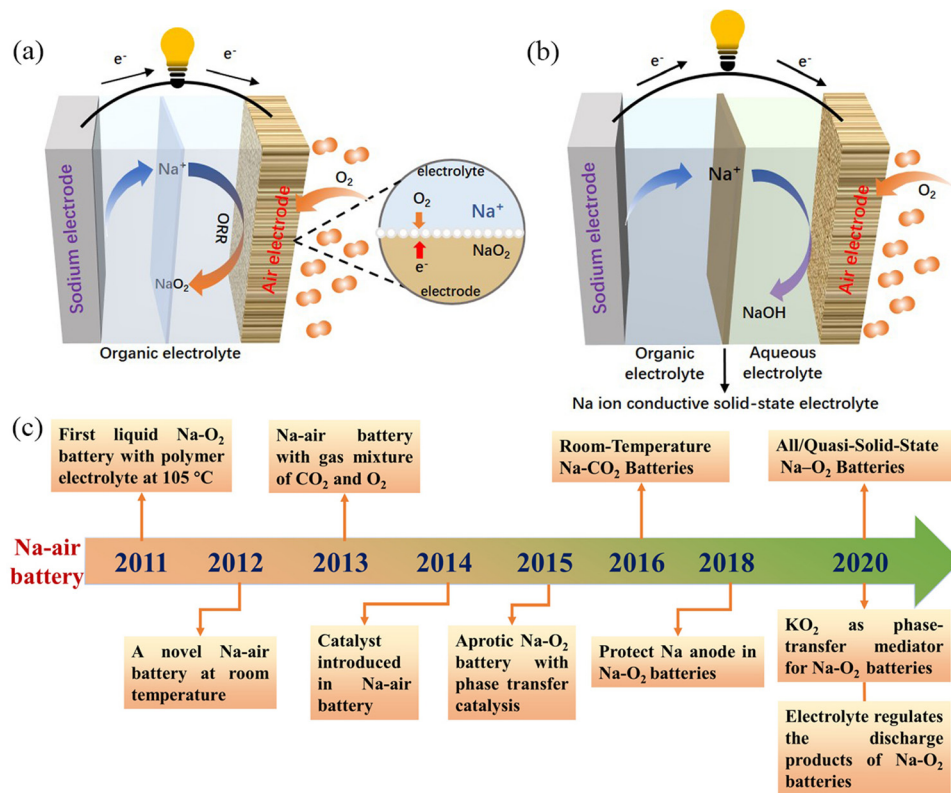**Fig. 1** Schematic illustration of the operation of: (a) organic Na–air batteries, and (b) hybrid Na–air batteries, (c) the chronology of major events concerning the development of Na–air batteries in the last decade.




nucleophilically attack the C atoms within the CH₂ group, resulting in by-products such as sodium carbonate (Na₂CO₃).^{28,40} At present, ethers are often chosen as electrolyte solvents, and these include dimethyl ether (DME), diethylene glycol dimethyl ether (DEGDME), and tetraethylene glycol dimethyl ether (TEGDME). Compounds often selected as electrolyte salts include sodium hexafluorophosphate (NaPF₆), sodium perchlorate (NaClO₄), sodium trifluoromethyl sulfonate (NaSO₃CF₃), and sodium bis(trifluoromethanesulfonyl) imide (NaTFSI), but the type and concentration of electrolyte salts affects the performance of Na–O₂ batteries. Lutz *et al.*⁴¹ showed that the anion in the dimethyl ether solvent had no significant effect on the formation of discharge products. However, PF₆[−] forms a stable solid electrolyte interface (SEI), while the SEI formed by TFSI[−] gradually increases with the cycling process, increasing the battery impedance. At the same time, increasing the concentration of electrolyte salt will increase the electrolyte viscosity, resulting in a decrease in both oxygen solubility and ionic conductivity, which has a negative impact on the electrochemical performance of the battery.⁴² The hybrid electrolyte Na–air batteries contain two electrolytes with the anode and cathode being immersed in organic and aqueous electrolytes, respectively. The diaphragm in the middle of the battery is a sodium ion-conductive solid electrolyte membrane which prevents oxygen and moisture diffusion into the negative compartment. This allows only the unidirectional transport of sodium ions to the negative compartment, preventing the anode from suffering unwanted oxidative reactions.⁴³ The main component of the solid electrolyte is Na₃Zr₂Si₂PO₁₂ (NASICON).^{44,45} The electrolyte in the positive compartment (anode side) is the same as that for the organic Na–O₂ battery, while the negative compartment (cathode side) typically has aqueous electrolyte with NaOH as the solute.⁴⁶ The two energy storage mechanisms are absorption and gas release at the air cathode during charging and discharging, corresponding to the oxygen reduction reaction (ORR) and oxygen evolution reaction (OER), respectively.^{22,34,47–49}

2.1. Organic Na–air batteries

Because of the similarity in chemical properties of metallic Li and Na, organic Na–air batteries share the same reaction mechanism as Li–O₂ batteries with regard to energy storage. The Li⁺ produced during the discharge of Li–O₂ batteries is not able to stabilize the highly active O₂[−] and therefore the lithium peroxide formed is the main discharge product of Li–O₂ batteries.²⁵ This is because Na⁺ is softer and has a higher polarizability compared to Li⁺, which can effectively stabilize O₂[−]. Thus, the main discharge product of Na–O₂ battery is NaO₂. However, a variety of discharge products have been seen during research under different experimental conditions and these include Na₂O₂,^{50,51} Na₂O₂·2H₂O,⁵² or mixtures,^{53,54} and their corresponding chemical reactions are shown in eqn (4)–(9).³²



or



where E_0 is the standard electrode potential.²² The potentials for the formation of the two sodium oxides are close, so the competition for forming NaO₂ and Na₂O₂ during the discharge of organic Na–O₂ batteries is fierce. Up to now, the discussion of the main products formed during the discharge of Na–air cells has been inconclusive, and this is owing to the close values for the free enthalpy of formation of these products. At 298 K, the free enthalpy of formation of NaO₂ (−437.5 kJ mol^{−1}) is slightly smaller than that of Na₂O₂ (−447.9 kJ mol^{−1}), with the latter being thermodynamically more stable than NaO₂.⁵⁵ However, the free enthalpy difference between the two sodium oxides is only 12.2 kJ mol^{−1} and it is difficult to distinguish whether the superoxide and peroxide will be the dominant discharge product in practice since local compositional inhomogeneities are the determining factor.⁵⁵ Kang *et al.*⁵⁶ showed that the thermodynamic stability of sodium oxides depends on the material's particle size, which determines the competition between bulk and surface energies. NaO₂ is relatively more stable as it has lower surface energy at nanoscale sizes due to the competition between surface and bulk energy. However, to ensure a long cycle life and excellent electrochemical performance of organic Na–O₂ cells, they should have a low overpotential and a high OER activity. Therefore, generating NaO₂ as the main discharge product of organic Na–air batteries is necessary. The reason is that the NaO₂ decomposition process involves a single electron transfer process, which requires a low overpotential to complete; however, the peroxide-dominated discharge product involves a two-electron transfer in the charging process, which requires a higher overpotential.^{34,43} Table 2 shows the main discharge products and overpotentials of different air cathodes and the results show that the overpotential of the cell is generally less than 1000 mV when NaO₂ is the main discharge product, while the overpotential of the cell is generally greater than 1000 mV when Na₂O₂ is the main discharge product. In addition, the low solubility of NaO₂ in the electrolyte and its poor dissolution ability also result in a small overpotential during charging.⁵⁷ Meanwhile, the low ionic and electronic conductivity of peroxide (*ca.* 10^{−20} S cm^{−1}) leads to slower OER kinetics, resulting in the generation of higher overpotential.^{34,57}

Two generation mechanisms, known as solution-mediated and surface-mediated, have been proposed to explain the NaO₂ crystal formation process for understanding the reaction mechanisms in Na–air batteries. In 2015, Janek *et al.*⁵⁸ used theoretical calculations to show that perfect NaO₂ crystals are insulating at room temperature with a band gap of 2.0 eV and their lower electronic conductivity (*ca.* 10^{−19} S cm^{−1}) was not sufficient for direct electrochemical deposition. They designed a two-electrode device to observe NaO₂ dissolution behaviour and observed NaO₂ decomposition during charging at an electrode that was not in contact with the fully discharged



Table 2 Summary of the electrochemical performance of carbon-based electrodes used in Na–O₂ batteries

| Cathode | Electrolyte | Current density/ mA g ⁻¹ | Initial discharge capacity/ mA h g ⁻¹ | Overpotential/ (mV) | Discharge product | Ref. |
|---|---|--|--|------------------------|--|------|
| Carbon thin films | 1 M NaPF ₆ /EC:DMC(1:1) | 1/10C | 1884 | 1500 | Na ₂ O ₂ | 28 |
| Carbon nanotube paper | 0.5 M NaSO ₃ CF ₃ /DEGDME | 500 | 7530 | 200 | Na ₂ O ₂ 2H ₂ O | 52 |
| Graphene nanosheets | 0.25 M NaPF ₆ /DME | 300 | 6208 | ~1600 | Na ₂ O ₂ | 51 |
| Reduced graphene oxide | 1.0 M NaSO ₃ CF ₃ /DEGDME | 500 | 11 935.3 | ~300 | Na ₂ O ₂ | 14 |
| Porous carbon spheres | 0.5 M NaSO ₃ CF ₃ /DEGDME | 500 | 16 500 | ~400 | NaO ₂ | 76 |
| Vertically aligned carbon nanotubes | 0.5 M NaSO ₃ CF ₃ /TEGDME | 67 | 4100 | ~200 | NaO ₂ | 72 |
| Nitrogen-doped graphene | 0.5 M NaSO ₃ CF ₃ /TEGDME | 75 | 8600 | — | Na ₂ O ₂ | 50 |
| Graphene aerogel | 0.1 M NaClO ₄ /DME | 100 | 6.61 mA h cm ⁻² | ~350 | NaO ₂ | 77 |
| Nitrogen-doped graphene aerogels | 0.3 M NaSO ₃ CF ₃ /DEGDME | 100 | 10 905 | ~1000 | Na ₂ O ₂ | 78 |
| Nitrogen-doped carbon | 0.5 M NaSO ₃ CF ₃ /TEGDME | 200 | 5905 | ~1000 | Na ₂ O ₂ , NaO ₂ | 79 |
| Nitrogen-doped nanofibers | 0.5 M NaSO ₃ CF ₃ /TEGDME | 100 | 8554.7 | 500 | NaO ₂ | 11 |
| Nitrogen doped carbon nanotubes on carbon paper | 0.5 M NaSO ₃ CF ₃ /DEGDME | 0.1 mA cm ⁻² | ~1350 | — | NaO ₂ | 71 |
| Nitrogen-doped carbon nanotubes | 0.5 M NaSO ₃ CF ₃ /DEGDME | 25 | 1887 | ~300 | Na ₂ O ₂ , NaO ₂ | 54 |
| Boron-doped onion-like carbon | 1.0 M NaSO ₃ CF ₃ /TEGDME | 0.15 mA cm ⁻² | 10 200 | ~1300 | Na _{2-x} O ₂ | 75 |
| Reduced graphite oxide | 1.0 M NaSO ₃ CF ₃ /TEGDME | 0.05 mA cm ⁻² | ~3.75 mA h cm ⁻² | ~1700 | NaO ₂ | 65 |
| Boron-doped reduced graphite oxide | 1.0 M NaSO ₃ CF ₃ /TEGDME | 0.05 mA cm ⁻² | ~3.45 mA h cm ⁻² | ~1800 | NaO ₂ | 65 |
| Ordered mesoporous carbon | 0.5 M NaSO ₃ CF ₃ /PC | 100 | 7987 | ~1500 | Na ₂ O ₂ , Na ₂ CO ₃ | 53 |

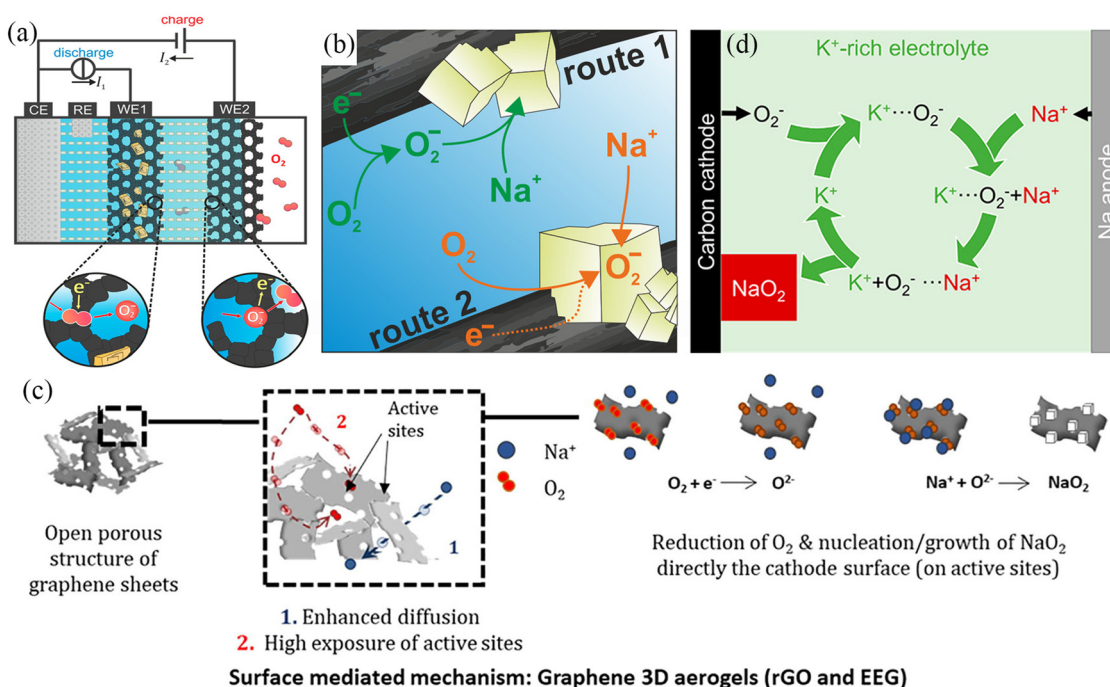


Fig. 2 (a) Schematic illustration of the dual-working electrode in Na–O₂ batteries. (b) Solution-precipitation route for NaO₂ growth in Na–O₂ batteries. (Reproduced from ref. 58 with permission from the American Chemical Society). (c) Schematic illustration of the surface-mediated mechanism of EEG electrode in Na–O₂ batteries. (Reproduced from ref. 47 with permission from the Science Press and Dalian Institute of Chemical Physics, Chinese Academy of Sciences. Published by ELSEVIER B.V. and Science Press.). (d) Schematic illustration of the mechanism using K⁺-rich electrolyte in Na–O₂ batteries. (Reproduced from ref. 61 with permission from the American Chemical Society).

electrode (Fig. 2a), demonstrating that superoxide dissolution occurs in the electrolyte and providing strong evidence for a solution-precipitation mechanism (Fig. 2b). Subsequently,

McCloskey's work⁵⁹ also showed that precipitation occurs when the dissolved NaO₂ reaches its solubility limit, yielding NaO₂ crystals of larger size. In 2022, the Ortiz-Vitoriano' group⁴⁷






observed that discharge products in graphene nanosheets showed uneven size distribution. At the initial discharge stage, the nucleating molecules are adsorbed on the graphene surface, which facilitates the nucleation of NaO₂ through a surface-mediated mechanism. However, as the discharge process progresses, the nucleation sites on the air electrode gradually become saturated, and the NaO₂ nucleation mechanism changes from a surface-mediated mechanism to a solution-mediated mechanism, forming larger NaO₂ cubes (Fig. 2c). As a result, discharge products have an uneven size distribution. Apart from the solution-mediated and surface-mediated mechanisms described above, there are also solution-mediated mechanisms based on phase transfer agents. As the most common phase transfer agent, water provides protons for the formation of intermediate HO₂, which then reacts with Na⁺ ions to produce precipitated NaO₂.⁶⁰ However, water can cause irreversible damage to the metal anode and generate a series of side reactions to increase the overpotential. Therefore, Lee *et al.*⁶¹ used potassium superoxide (KO₂), which is more chemically active and stable against NaO₂ and Na metal compared to water, as the phase transfer agent (Fig. 2d). At the same time, the electrochemical stability of KO₂ was superior to that of HO₂. The air batteries with KO₂ exhibited higher reversible specific capacity (more than 6 mA h cm⁻²) and longer cycle life (maintained for 25 cycles).

As mentioned earlier, organic sodium-air batteries with NaO₂ as the main discharge product usually show lower overpotential and more prominent cycling stability. To achieve a higher reversible specific capacity of sodium-air batteries, it is important to optimize and control the nucleation/growth mechanism of NaO₂ during the discharge process. Yang *et al.*⁶² investigated the relationship between the physical distribution and size of NaO₂ formed during the discharge process and the current density used. During a small current density discharge (10 mA g⁻¹), nano-sized (~50–500 nm) NaO₂ particles could be observed at the top, bottom, and sidewalls of the carbon nanotube (CNT) aggregate; however, during a high current density discharge of 1000 mA g⁻¹, micron-sized NaO₂ (~2 μm) appeared only at the top and bottom of the CNT aggregate. The reason for this difference is due to the higher local supersaturation of (O₂⁻-Na⁺)_n agglomerates with low migration rates during the fast discharge, which nucleate rapidly at the top and bottom of the CNT aggregate, while (O₂⁻-Na⁺)_n agglomerates nucleate more slowly and diffuse more uniformly at low discharge rates, yielding more uniformly sized NaO₂. In addition to the current density, the catalytic activity of the air electrode also has an obvious effect on the morphology and size of the discharge products. The bimodal transition metal oxide CaMnO₃ electrode with excellent catalytic activity precipitated nanoscale cubic particles during the discharge process, while the cubic particles completely disappeared during the subsequent charging process.⁶³ Alexis *et al.*⁶⁴ investigated the effect of different electrodes on the formation of NaO₂. The gas diffusion layer electrode formed discrete nano/micron NaO₂ cubes during discharge, whereas the gas diffusion layer electrode modified with Au formed NaO₂ flakes

at the same current density. This is because the strong interactions between Au and O₂/O₂⁻ increase the NaO₂ nucleation rate, leading to change in the growth process. Such a phenomenon was also observed in Chen's research.⁶⁵ Here, the boron-doped reduced graphene electrode covered by micron-scale RuO₂ showed a longer cycle life and better electrochemical performance relative to both the reduced graphene electrode and the boron-doped reduced graphene electrode; this behaviour was attributed the higher affinity between micron-scale RuO₂ and oxygen, while the amorphous Na_{2-x}O₂ is obtained at the end of the discharge. The RuO₂-modified CNT electrode forms a less crystalline discharge product, NaO₂, during the discharge process, while the morphology of the discharge product is drastically changed.⁶⁶ The present results have shown that nano-sized NaO₂ appears during the discharge process, which can be achieved not only by controlling the magnitude of current density during the discharge process, but also by selecting a suitable electrode type. Also the results show that no specific electrode type produces nano-sized NaO₂ during discharge; moreover, it seems that the better the electrocatalytic performance of the air electrode, the more likely nano-sized NaO₂ particles appear during discharge. There are two speculative reasons for these observations, on the one hand, the discharge products nucleate/grow quickly in the presence of highly catalytic of noble metal, while on the other hand, the highly active NaO₂ is easy to decompose during the *ex situ* testing process and the results obtained by using *in situ* testing technique will be more credible.

2.2. Hybrid Na-air batteries

Fig. 1b shows the schematic illustration of a hybrid Na-air battery. During the discharge process, sodium metal at the anode is oxidized to Na⁺, while Na⁺ migrates from the anode to the air cathode through the solid electrolyte and aqueous electrolyte, and thus, the ORR reaction occurs at the air cathode to obtain the discharge product NaOH.⁴⁵ In the subsequent charging process, the OER reaction occurs at the air cathode and electrons move from the cathode to the anode through the external circuit, while sodium metal is deposited on the anode. The chemical reaction equations involved in the discharge process are shown in eqn (10)–(12):



Hybrid Na-air batteries have a relatively simple reaction during energy storage and only one discharge product (NaOH) appears, significantly reducing side reactions and improving the cycle life. Meanwhile, the NaOH generated during discharge can be dissolved in the electrolyte, avoiding the accumulation of discharge products on the surface of the air cathode and improving the cycle efficiency. The cathode compartment electrolyte in the hybrid Na-air battery is NaOH solution, so the battery's output voltage can be controlled by adjusting the pH



of the solution. The output voltage can be obtained from the Nernst equation, as shown in eqn (13):

$$E = E^{\circ} - \frac{RT}{nF} \cdot \ln \frac{[\text{Red}]}{[\text{Ox}]} \quad (13)$$

where E is the battery output voltage, E° is the output voltage of the battery under standard conditions, R is the gas constant, T is the temperature (K), n is the electron transfer number, F is the Faraday constant, $[\text{Red}]$ is the concentration of the reducing species, $[\text{Ox}]$ is the concentration of the oxidized species. When the pH value changes by one unit, the voltage changes by 59 mV.⁴⁵ Compared to organic Na–O₂ batteries that require dry oxygen to prevent the generation of by-products, hybrid Na–air batteries can be used without providing pure oxygen. In addition, hybrid Na–air batteries can provide higher theoretical voltages⁴⁴ and involve a four-electron transfer reaction. This makes them ideal for synthesising high-energy density and high power-density rechargeable batteries. Nevertheless, the cycling stability, overpotential, power density, and energy density of the hybrid Na–air battery are mainly determined by the strength of NASICON in the electrolyte. Hayashi *et al.*⁶⁷ assembled a hybrid Na–air battery with NASICON as the separator, an organic solvent as the anode compartment electrolyte, and 1.0 M NaOH as the cathode compartment electrolyte. The morphology of the NASICON ceramic sheets did not change significantly after soaking in the two electrolytes for two days. Meanwhile, the X-ray diffraction (XRD) results of NASICON after charge/discharge showed that the NASICON phase remained stable. In addition, the morphology and phase structure of NASICON did not change significantly after stable cycling in 5.0 M NaOH for 750 cycles at a current density of 1.0 A g⁻¹.⁶⁸ The above results show that NASICON-based separators are stable in humid environments. However, the contact between the rigid NASICON separator and the sodium metal anode is not tight, which increases the battery's internal resistance. At the same time, sodium dendrite growth is also a safety issue during the cycling process. Hui *et al.*¹⁷ prepared liquid anodes by dissolving sodium metal in TEGDME. In this case, liquid-to-solid contact was better than solid-to-solid contact, which reduced cell resistance. Hybrid Na–air batteries based on liquid anodes exhibited lower overpotential (140 mV) and long cycle life (more than 500 cycles).

In summary, both organic Na–air batteries and hybrid Na–air batteries show bright application prospects. Sodium alkali metal reacts very violently with water, and thus organic Na–air batteries adopt organic electrolytes in both positive and negative chambers, thus improving the safety of organic sodium–air batteries. However, organic electrolytes are more expensive and prone to environmental pollution and have other associated problems. At the same time, the products formed during the discharge process of organic Na–air battery will be deposited on the surface of air electrode and gradually cover the redox active sites causing the degradation of the overall electrochemical performance of the battery. Moreover, the application conditions of organic Na–air batteries are relatively harsh, requiring dry oxygen source and gas purification devices in order to avoid

the occurrence of side reactions, which will greatly increase the costs of application. Compared with organic Na–air batteries, hybrid Na–air batteries can directly use air as the oxygen source, which greatly reduces the costs. The products formed during the discharge process of hybrid Na–air batteries can be dissolved in the electrolyte of the cathode chamber, avoiding the degradation of battery electrochemical performance due to the accumulation of discharge products. Therefore, the hybrid Na–air battery exhibits low overpotential, high energy density (NaOH: 2090 W h kg⁻¹; NaO₂: 1105 W h kg⁻¹, Na₂O₂: 1602 W h kg⁻¹, Na₂O: 1687 W h kg⁻¹) and long cycle life. NASICON is an important component of the hybrid Na–air battery, which mainly separates the anode chamber and the cathode chamber, but the lower ionic conductivity of NASICON is not beneficial to the adequate operation of the air battery. The interfacial interaction between NASICON and the electrolyte needs to be further investigated, as it affects the internal resistance of the whole cell. For organic Na–air batteries and hybrid Na–air batteries, the rational design of the air cathode is the key to increase the comprehensive electrochemical performance of the battery. The air cathode is essentially a bifunctional catalyst with good OER/ORR activity. In addition to the bifunctional catalytic performance, the air electrode should be porous to facilitate gas diffusion and ion transport, which also expands the area for electrocatalytic reactions. The rational use of organic electrolytes and solute salts will promote the formation of stable SEI on the anodic side and thus further contribute to improving the air battery performance.

3. Air cathode materials

3.1. Carbon materials

An ideal air cathode material should have high surface area and abundant pore distribution in order to: (1) maximise the contact between the electrolyte and the electrode, (2) fully utilize the active sites during the charging/discharging cycling, and (3) provide sufficient space to accommodate the discharge products (NaO₂ and Na₂O₂). Carbon-based materials are widely used as cathode materials for Na–O₂ batteries owing to their excellent physicochemical properties,^{11,22,31,69} including (i) large specific surface area, which exposes abundant redox active sites and accommodates higher amounts of discharge products at the same time; (ii) porous structure that facilitates full electrolyte infiltration and structural stability, while promoting oxygen diffusion; (iii) excellent electronic conductivity that facilitates electron transport, and (iv) low cost for high-volume fabrication. Carbon cloth and carbon paper have been used as cathode materials for metal–O₂ batteries due to their low costs, but their poor cycling stability and limited specific capacity have restricted further applications.⁷⁰ In recent years, a large number of carbon materials with different dimensions have been elaborately designed, such as two dimensional (2D) carbon thin film,²⁸ CNT,^{31,54,71,72} carbon nanofiber (CNF),^{11,73,74} porous carbon spheres,^{75,76} graphene,^{50,51,77,78} reduced graphene oxide¹⁴ and porous carbon,^{53,79} and these



have been widely used as cathode materials for Na–O₂ batteries. Detailed information on carbon materials and their electrochemical performances are provided in Table 2.

A novel Na–O₂ battery design based on a carbon film cathode (Fig. 3a) was reported by Fu *et al.*²⁸ The carbon thin film electrode exhibited a high specific capacity of 3600 mA h g⁻¹ at a discharge rate of 1/60C at room temperature (Fig. 3b), which was significantly higher than the specific capacity exhibited by conventional cell cathode materials. The main discharge product was Na₂O₂, with Na₂CO₃ and NaOCO-R found in the fully discharged electrode, and these resulted from the decomposition of the electrolyte. Carbonate-based electrolytes are easily decomposed during cycling, forming many by-products ($n\text{Na}^+ + \text{O}_2 + \text{EC/DEC} + ne^- = \text{Na}_2\text{CO}_3 + \text{NaOCO-R} + [\text{side products}]$), which are known to affect the cycling stability of Na–O₂ batteries. In 2014, Zhou *et al.*⁵² used carbon nanotube paper as cathode material in Na–O₂ batteries with a discharge-specific capacity of up to 7530 mA h g⁻¹. This reduced the reaction depth and improved the cycling performance of Na–O₂ cells when the cut-off capacity is limited to 1000 mA h g⁻¹, while the overpotential was as low as 200 mV (Fig. 3c); the XRD results showed that Na₂O₂·2H₂O was the main discharge product. Oxygen-containing functional groups on the electrode material surface play a key role in the electrochemical reaction mechanism of the metal–O₂ cell. Sun's group⁷³ controlled the air electrode's surface properties to investigate the effect of oxygen-containing functional groups on the composition and morphology of the discharge production (Fig. 3d). Hydrophobic and hydrophilic (containing a large number of oxygen-containing functional groups) carbon materials follow different reaction mechanisms in the discharge processes. During the discharge process, NaO₂ crystal particles are formed on the

hydrophobic cathode, but the presence of trace water in the electrolyte and the instability of NaO₂ lead to the rapid transformation of NaO₂ to Na₂O₂·2H₂O and NaOH (Fig. 3e). Na₂O₂·2H₂O, carbonate and other layered discharged products are formed on the hydrophilic cathode (Fig. 3f). Therefore, to ensure that the main discharge product of Na–O₂ battery is NaO₂, the water content of the battery electrolyte and the surface chemistry of the air electrode should be strictly controlled. Thus, controlling the discharge product composition during the discharge of Na–O₂ battery is critical to improving the cycling stability.

Carbon nanotubes are a class of widely investigated carbonaceous materials which have a very bright prospect for use as the air cathode of Na–O₂ batteries. In 2021, Wang *et al.*³¹ directly used CNTs as a cathode of Na–O₂ batteries with different concentrations of ether-based electrolytes (NaCF₃SO₃/TEGDME). The results showed that the Na–O₂ batteries exhibited excellent cycling stability (Fig. 4d) in the saturated electrolyte (1.6 M NaCF₃SO₃/TEGDME), and the battery cycling stability increased by four times. Scanning electron microscope (SEM) imaging was used to observe the morphologies of the CNT cathode with the same cut-off capacity at different electrolyte concentrations (Fig. 4a–c). The results showed that the amount of the discharge product increased with the electrolyte concentration suggesting a gradual decrease in the formation of the dissolved discharge product. This was confirmed by the results obtained from the UV/Vis absorption spectra of the discharge products. On immersing the CNT cathode in TiOSO₄ solution after cycling at different electrolyte concentrations, it was observed that the solution colour and absorbance increased with the electrolyte concentration (Fig. 4e and f), suggesting a gradual increase of the discharge product content

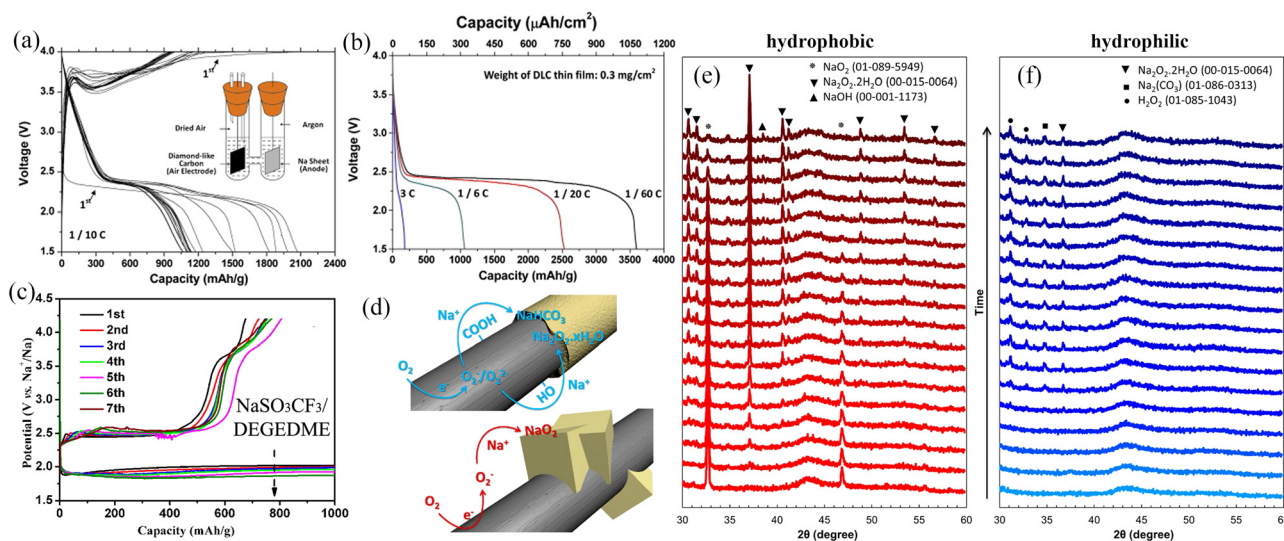


Fig. 3 (a) Galvanostatic discharge/charge curves of the carbon thin film/Na cell at the current rate of 0.1C. The inset shows the composition of the Na–air cell (b) discharge profiles of carbon thin film/Na cell at different current rates. (Reproduced from ref. 28 with permission from the Elsevier). (c) The discharge/charge curves with a limiting capacity of 1000 mA h⁻¹ in the 0.5 M NaSO₃CF₃/DEGEDME electrolyte with CNT papers as a cathode. (Reproduced from ref. 52 with permission from the Elsevier). (d) Schematic diagram of the formation of discharge products on the surface of carbon-based materials with different chemical properties during the discharge process. The XRD results for hydrophobic (e) and hydrophilic (f) air electrodes discharge in Na–O₂ cells. (Reproduced from ref. 73 with permission from the American Chemical Society).



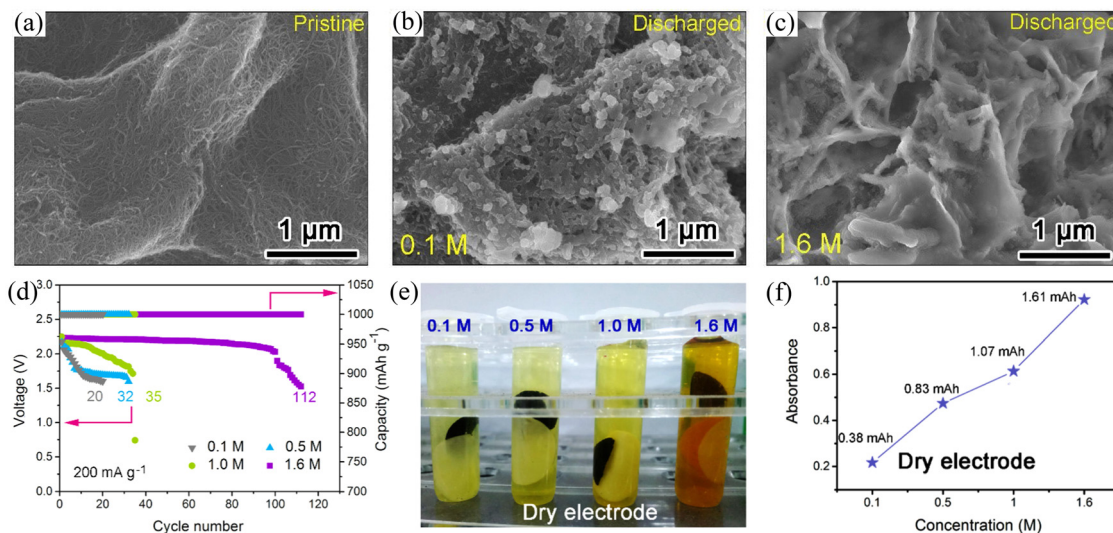


Fig. 4 SEM images of (a) the pristine CNT cathode and the discharged CNT cathodes under the same discharge capacity in $\text{NaCF}_3\text{SO}_3/\text{TEGDME}$ electrolyte at concentrations of (b) 0.1 M and (c) 1.6 M. (d) The long-term cycling performance of Na- O_2 battery using CNT cathode in different concentrations of $\text{NaCF}_3\text{SO}_3/\text{TEGDME}$ electrolyte. (e) Optical image of the dry CNT cathodes soaking in TiOSO_4 solution after discharge to the same capacity in different $\text{NaCF}_3\text{SO}_3/\text{TEGDME}$ electrolyte concentrations, and (f) the corresponding absorbance as a function of concentration. (Reproduced from ref. 31 with permission from Elsevier).

on the CNT cathode. At the same time, the oxygen content in the saturated electrolyte solution decreased dramatically, effectively reducing the Na electrode's oxidation level. Shao-Horn *et al.*⁶² observed that the size and distribution of Na- O_2 batteries discharge products were highly dependent on the discharge rate. Both micron-sized and nano-sized NaO_2 were formed at low discharge rates and were uniformly distributed inside and outside the carbon nanotubes; however, at a high discharge rate, micron-sized NaO_2 was only distributed at the ends of the carbon nanotubes. This is due to the fact that sodium ions will firstly form $\text{O}_2^- \text{--} \text{Na}^+$ small molecules during the discharge process, and then these small molecules will relocate in the electrode material. The $\text{O}_2^- \text{--} \text{Na}^+$ small molecules will diffuse uniformly inside the anode material at low current densities instead of gathering rapidly to form NaO_2 and the discharge products will grow slowly and be distributed more uniformly. However, $\text{O}_2^- \text{--} \text{Na}^+$ small molecules will gradually gather to form $\text{O}_2^- \text{--} \text{Na}^+$ aggregates, which have weaker migration ability compared to $\text{O}_2^- \text{--} \text{Na}^+$ small molecules and thus will not be able to diffuse rapidly under high current density. This reduces the utilization of the active material and the battery capacity decay is more significant. The structure of the active material of the battery electrode has a remarkable influence on the electrochemical performance, particularly in the case of structurally diverse graphene-based carbon materials. At the same time, the electrochemical reactions, structural transformations and kinetics relevant to the charging and discharging of the materials should be explored in detail, which is necessary for the construction of high energy density Na- O_2 batteries.

Graphene is another widely used electrode material for rechargeable batteries. In 2013, Fu *et al.*⁵¹ used graphene nanosheets as Na- O_2 battery cathodes for the first time and

this led to an ultra-high discharge capacity of 6208 mA h g^{-1} at a current density of 300 mA g^{-1} , which was three times higher than that of carbon electrode (2030 mA h g^{-1}). At the same time, the graphene nanosheet electrode exhibited a lower overpotential compared to the thin film electrode. The above results indicate that graphene nanosheets are a promising candidate as cathodes for Na-air batteries. Air cathodes undergo gas transport and substance exchange during the charging/discharging process, so the porosity of the air cathode plays a critical role in the performance. The main technical challenge with graphene is the stacking of the nanosheets, which causes a considerable reduction of active sites and hinders oxygen gas diffusion, leading to rapid capacity decay. Ortiz-Vitoriano *et al.*⁷⁷ investigated the electrochemical behaviour of reduced graphene aerogels with different porosities. The ArGO-N (randomly 3D oriented sheets) electrode exhibited a high discharge capacity of $6.61 \text{ mA h cm}^{-2}$ at a current density of 100 mA g^{-1} , which is higher than that of the ArGO-U (3D oriented sheets) cathode ($1.72 \text{ mA h cm}^{-2}$) and film (stacked sheets) cathode ($0.06 \text{ mA h cm}^{-2}$) (Fig. 5a). The disordered arrangement of nanosheets in ArGO-N exhibits more active sites providing large pore volumes and a suitable pore size distribution, which enhances material diffusion and exchange and promotes redox reactions (Fig. 5c). As a result, the ArGO-N electrode showed high stability after 39 cycles at a cut-off discharge capacity of 0.5 mA h cm^{-2} with a low overpotential of 250 mV (Fig. 5b). In addition, Sun *et al.*¹⁴ prepared a hierarchically porous reduced graphene oxide air battery cathode (Fig. 5d). This air electrode has a continuous network-like framework and suitably sized open pores, which facilitates fluent gas transport and ensures efficient utilization of the active sites (Fig. 5e). The small open pore-containing electrode (3DP-SP) exhibited a high discharge-specific capacity



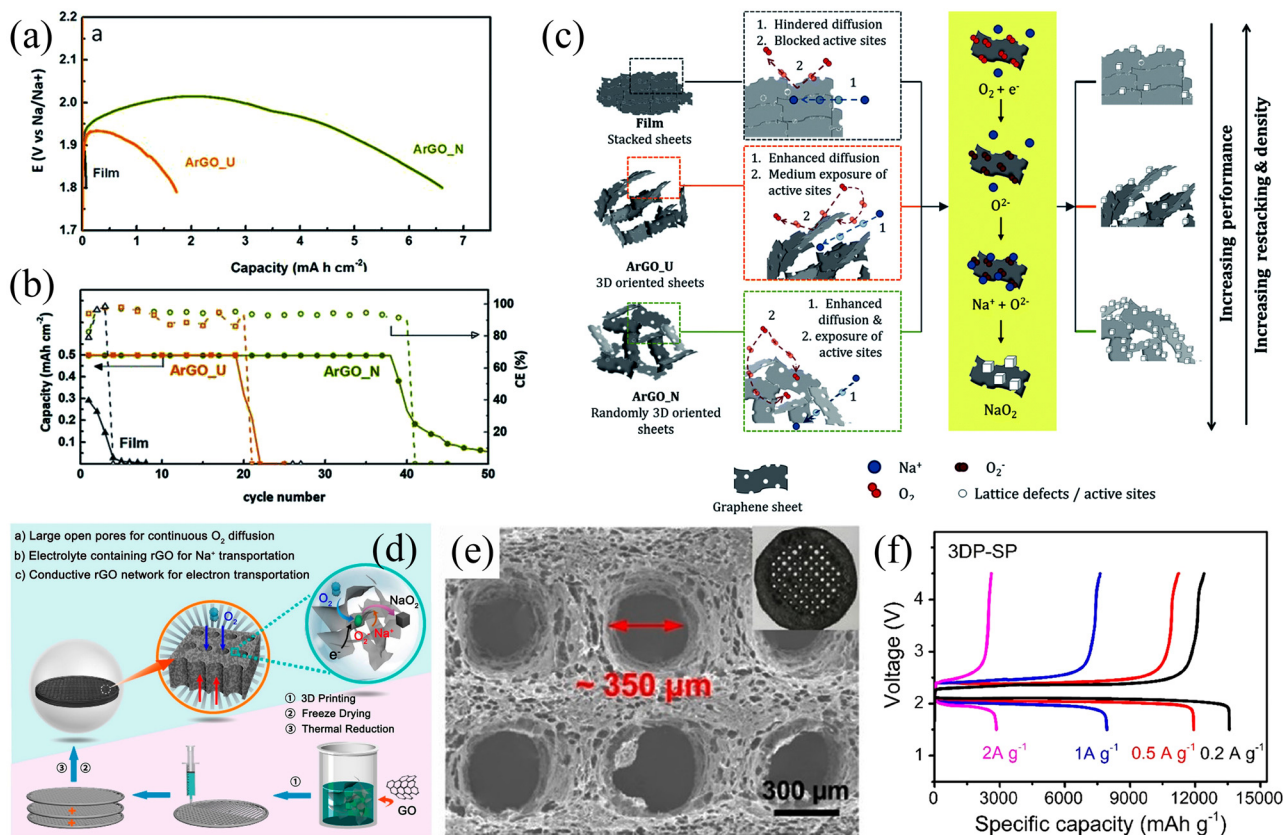


Fig. 5 (a) Discharge curves of three different electrodes at the current density of 100 mA g⁻¹. (b) The evolution of discharge capacity and Coulombic efficiency with the number of cycles for the three different electrodes. (c) Schematic illustration of the proposed mechanism for the three different electrodes. (Reproduced from ref. 77 with permission from the Royal Society of Chemistry). (d) Schematic illustration of the 3D-rGO air electrodes for Na-O₂ battery. (e) SEM image of the 3DP-SP sample. (f) The initial discharge/charge curves of 3DP-SP cathodes at current density. (Reproduced from ref. 14 with permission from the American Chemical Society).

of 13 484.6 mA h g⁻¹ at a current density of 200 mA g⁻¹ (Fig. 5f). SEM images demonstrate that the discharge product NaO₂ was uniformly distributed on the inner and outer sides of the 3DP-SP electrode due to the open pore channels on the electrode. The electrode also exhibited excellent cycling stability with a cut-off capacity of 500 mA h g⁻¹ at a current density of 500 mA g⁻¹ for 120 stable cycles. This work also suggests that the pore size in the air electrode has a significant effect on the performance of the air battery and that an oversized pore channel can reduce the effective mass of the electrode active material, leading to a degradation of the battery performance.

In addition to various graphene-based electrode materials, porous carbon spheres (PCS) with high specific surface area have also been applied for use in Na-O₂ batteries. Fig. 6a shows a schematic illustration of the synthesis of hierarchical PCS.⁷⁶ The porosity of PCS can be precisely modulated and the pores inside and outside of PCS facilitate the diffusion of oxygen and the infiltration of electrolytes (Fig. 6b). The PCS cathode has a high specific capacity of 16 500 mA h g⁻¹ in the initial cycle at a current density of 500 mA g⁻¹, while it can be stably cycled for 150 cycles at a high current density of 2.0 A g⁻¹ (Fig. 6c). More interestingly, the discharge product NaO₂ is not precipitated in

the form of cubic particles but was deposited on the surface of PCS in the form of a conformal film (Fig. 6d).

The catalytic activity of the material is mainly measured by the overpotential and stability of the catalyst. The carbon films show excellent catalytic activity, but the restricted specific surface area and active sites are not conducive to achievement of high catalytic activity. The development of carbon materials such as CNT, graphene oxide (GO), PCS with high specific surface area, abundant active sites and pores, have resulted in the materials showing higher reversible specific capacity and cycle life compared to carbon films. However, pure carbon materials show poor catalytic activity, with both experimental work and theoretical calculations proving that nitrogen doping can improve the electronic conductivity and catalytic activity of carbon materials leading to these electrodes exhibiting higher capacity, lower overpotential and longer cycle life.¹¹ In addition, the presence of nitrogen heteroatoms is conducive to the uniform deposition of discharge products on the electrode surface, preventing pores from being blocked by granular products, and improving the long cycle life of the electrode.^{11,22,71,80} In 2013, Sun *et al.*⁵⁰ introduced nitrogen atoms into graphene nanosheets, which resulted in superior



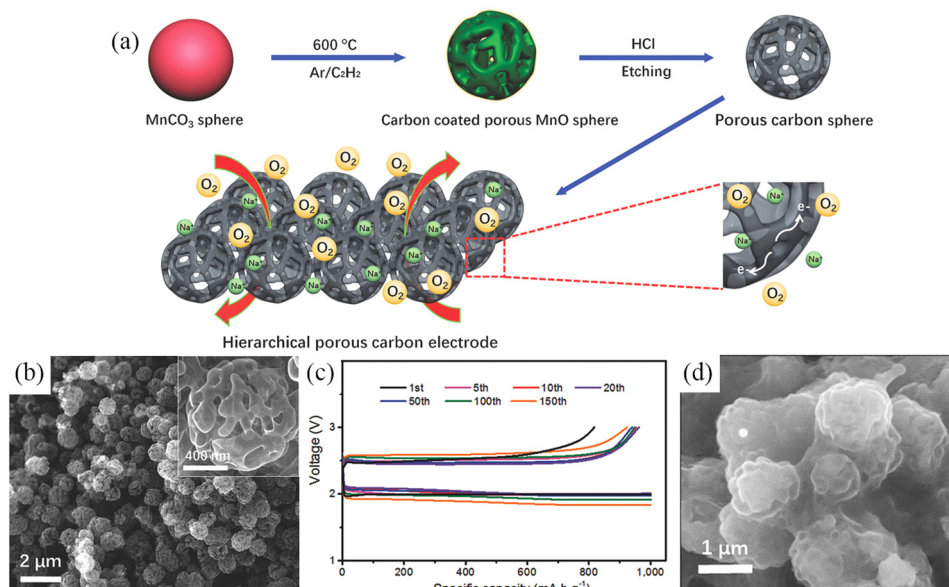


Fig. 6 (a) Schematic illustration of the synthesis processes of PCS. (b) SEM images of PCS; The inset is a high magnification SEM image of the PCS. (c) Cycling at 2.0 A g⁻¹ while curtailing the capacity to 1000 mA h g⁻¹ and (d) SEM image of discharged PCS electrode. (Reproduced from ref. 76 with permission from the WILEY).

electrochemical performance. This is due to the introduction of more active sites by nitrogen doping, resulting in smaller particle sizes and a more uniform distribution of the discharge products. Zhang's team⁷⁹ prepared nitrogen-doped carbon (NC) using nitrogen-containing precursors. This process resulted in increased nitrogen content, increased specific surface area, and introduction of multi-sized pores (Fig. 7a). Electrochemical results showed that the NC with the optimized structure showed high catalytic activity, enhanced specific discharge capacity (6905 mA h g⁻¹) and good cycle life (66 cycles) (Fig. 7b). In 2021, Wang *et al.*¹¹ introduced nitrogen atoms into

carbon nanofibers derived from polypyrrole (NCF) as an air cathode for Na–O₂ batteries. The air cathode exhibited a low overpotential of 500 mV, a high specific capacity of 8554.7 mA h g⁻¹ (Fig. 7c), and high stability after 90 cycles with NaO₂ as the discharge product. The excellent electrochemical performance stems from the three-dimensional network structure with high electronic conductivity, specific surface area, and catalytic activity. The highly reactive N-groups optimize the surface adsorption energies of reactants and intermediates while controlling the uniform deposition of discharge products at the nanoscale (Fig. 7d). Notably, the heteroatoms

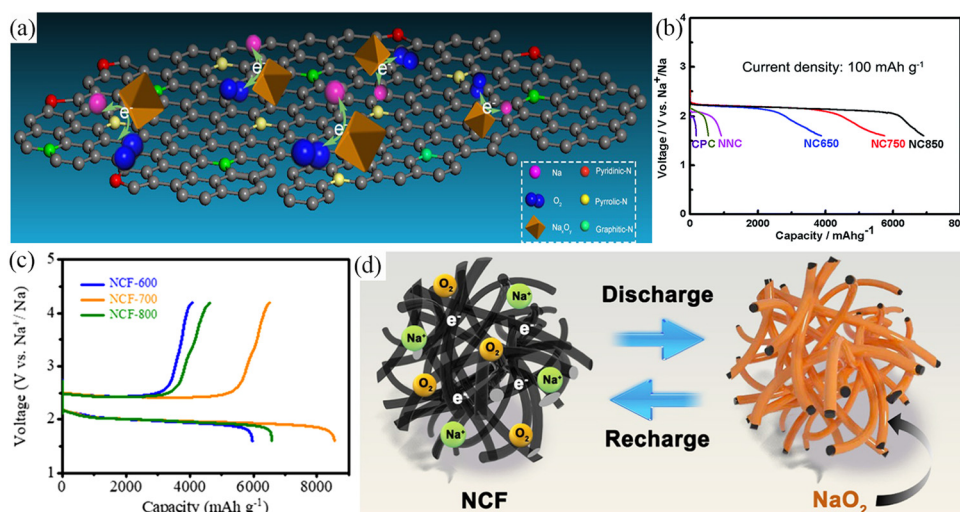


Fig. 7 (a) Illustration of the decomposition of discharge products on N-doped carbon cathodes. (b) The discharge curves for Na–O₂ battery with six different electrodes at current density of 100 mA g⁻¹. (Reproduced from ref. 79 with permission from the Royal Society of Chemistry). (c) The discharge/charge profiles of the different NCF cathodes at 100 mA g⁻¹. (d) Schematic illustration of the formation of discharge products (film-like layer NaO₂) on NCF electrode surface during the discharge/charge process. (Reproduced from ref. 11 with permission from the Elsevier).



doped in the preceding work were only nitrogen atoms and multi-heteroatom doping is expected to significantly improve the catalytic activity of the carbon materials. In addition, Pozo-Gonzalo and coworkers⁸¹ prepared multi-heteroatom-doped (S, N, and F) multilayer fibrous network-like structures. Owing to the promotion of oxygen adsorption and the synergistic effect of the different heteroatom dopants, the ORR activity during the discharge process was enhanced, and the discharge-specific capacity was effectively increased (0.35 mA h cm⁻² at 0.6 mA cm⁻²). The catalysts showed excellent OER/ORR catalytic activity arising from the synergistic effect of heteroatom codoping and mesoporous carbon structure. The heteroatom codoping delivered a novel strategy for preparing a new generation of high-performance free-standing binder-free carbon-based air cathodes. These air cathodes have been assessed for Na-O₂ batteries in a hybrid electrolyte composed of diglyme and ionic liquid and presented excellent long-term cycling (157 cycles). This value was higher than the case where only diglyme was used as an electrolyte.

3.2. Transition metal and metal oxides

Transition metals (TMs) and metal oxide (TMOs) catalysts are promising candidates for Na-O₂ batteries. This is owing to these materials being inexpensive, environmentally friendly, and having remarkable catalytic activity when used in a wide range of electrolytes (aqueous and organic). Various transition metal-based catalysts have been widely used in Na-O₂ cells such as transition metal compounds (CoB,⁸² CoP,¹⁵ and SnS₂⁸³), TMOs (CoO,¹⁵ Co₃O₄,^{15,35,84,85} Mn₂O₃,⁸⁶ α-MnO₂,⁸⁷ and VO₂@rGO-carbon paper⁸⁸) and transition metal composites (Co@ECNCFs).²⁷ The electrolyte media includes NaOH, DME, TEGDME, and DEGDME. Detailed information related to transition metals and metal oxides and their electrochemical performance as cathodes is shown in Table 3.

In 2018, Yan *et al.*⁸² applied a solid-phase method for the controllable synthesis of porous CoB nanosheets (Fig. 8a). The CoB nanosheet cathode exhibited a high specific capacity of 11 482 mA h g⁻¹, low overpotential, and cycling stability of 74 cycles (Fig. 8b and c). The results obtained from theoretical calculations suggested that the excellent electrochemical performance can be attributed to the high electronic conductivity and unique porous structure of CoB. The abundant pores and larger specific surface area provide more catalytically active sites and O₂/electrolyte diffusion channels, making such materials ideal for OER and ORR. Subsequently, Ko *et al.*⁸³ synthesized 3D-structured SnS₂ nanosheets using the solvothermal method as cathodes for Na-O₂ batteries with mixed electrolytes (Fig. 8d). All working electrodes were observed to work in alkaline solution. The 3D structure of the SnS₂ nanosheets provided paths for O₂ and electrolyte diffusion, while the high specific surface area provided sufficient active sites. The cell's performance was compared with the cells made by Pt/C and activated carbon as air electrodes. The total cell overpotential of 520 mV (Fig. 8e) was very close to the overpotential of 470 mV for the Pt/C air electrode at 5.0 mA g⁻¹ current density. When the current density was 240 mA g⁻¹, the power density was measured to be 300 mW g⁻¹, showing high stability after 40 cycles (Fig. 8f).

Since gas/liquid transport is involved in the charge/discharge process, the electrocatalyst morphology should be strongly anisotropic, reducing diffusion paths and improving electrochemical performance. Cho *et al.*⁸⁶ used a hydrothermal method to synthesize hollow double-walled Mn₂O₃ nanocubes, which maximized the diffusivity of electrolytes and oxygen, thus improving the gas-liquid transport processes (Fig. 9a-c). Moreover, the as-prepared Mn₂O₃ nanocubes possess ORR/OER bifunctional catalytic activity and thus have great potential as SAB air cathode materials. The SABs exhibited an overpotential

Table 3 Summary of the electrochemical performance of the metallic compounds, TMOs, transition metal composites, perovskites, and spinel electrodes used in Na-O₂ batteries

| Cathode | Electrolyte | Current density/ mA g ⁻¹ | Initial discharge capacity/mA h g ⁻¹ | Overpotential/ mV | Discharge product | Ref. |
|--|--|--|--|----------------------|---|------|
| CoB | 0.5 M NaCF ₃ SO ₃ /TEGDME | 100 | 11 482 | ~600 | Na ₂ O ₂ , NaO ₂ | 82 |
| CoO/CoP | 0.5 M NaTFSI/TEGDME | 100 | 12 654 | ~650 | Na ₂ O ₂ 2H ₂ O | 15 |
| CNT@Co ₃ O ₄ | 0.5 M NaCF ₃ SO ₃ /DEGDME | 150 | ~710 | ~2100 | Na ₂ O ₂ , NaO ₂ | 84 |
| CNT/Co ₃ O ₄ | 0.5 M NaCF ₃ SO ₃ /DEGDME | 150 | ~555 | ~2100 | Na ₂ O ₂ , NaO ₂ | 84 |
| VO ₂ @rGO | 1.0 M NaCF ₃ SO ₃ /TEGDME//0.1M NaOH | 80 | 104 mW g ⁻¹ (power density) | 640 | NaOH | 88 |
| SnS ₂ | 1.0 M NaCF ₃ SO ₃ /TEGDME//0.1M NaOH | 5.0 | 300 mW g ⁻¹ (power density) | 520 | NaOH | 83 |
| MoS ₂ /CC | 0.5 M NaCF ₃ SO ₃ /TEGDME | 0.1 mA cm ⁻² | 1.55 mA h cm ⁻² | ~360 | Na ₂ O ₂ , NaO ₂ | 91 |
| α-MnO ₂ @graphene | NaCF ₃ SO ₃ /TEGDME//0.1M NaOH | 15 | — | 700 | NaOH | 92 |
| Mn ₂ O ₃ | 1.0 M NaCF ₃ SO ₃ /TEGDME//0.1M NaOH | 5.0 | 200 mW g ⁻¹ (power density) | 330 | NaOH | 86 |
| Co-ECNCFs | 0.5 M NaCF ₃ SO ₃ /TEGDME | 250 | ~5350 | 1170 | Na ₂ O ₂ | 27 |
| High-spin Co ₃ O ₄ | 0.5 M NaCF ₃ SO ₃ /TEGDME | 100 | — | ~60 | NaO ₂ | 35 |
| Co ₃ O ₄ nanowire on carbon textiles | 0.5 M NaCF ₃ SO ₃ /TEGDME | 100 | 4687.2 | ~1500 | Na ₂ O ₂ , NaO ₂ | 85 |
| CaMnO ₃ | 1.0 M NaCF ₃ SO ₃ /TEGDME | 100 | 9560 | ~1300 | Na ₂ O ₂ , NaO ₂ | 63 |
| NiCo ₂ O ₄ | 1.0 M NaClO ₄ /DME | 20 | 1762 | 960 | Na ₂ O ₂ | 93 |
| MnCo ₂ O ₄ /N-rGO | 1 M NaClO ₄ /EC:DMC (1:1) with 1 vol% FEC//1.0 M NaOH | 0.13 mA cm ⁻² | — | 390 | NaOH | 94 |
| C@NiCo ₂ O ₄ -NAs | 1.0 M NaClO ₄ /TEGDME | 50 | 6500 | 600 | Na ₂ O ₂ | 95 |



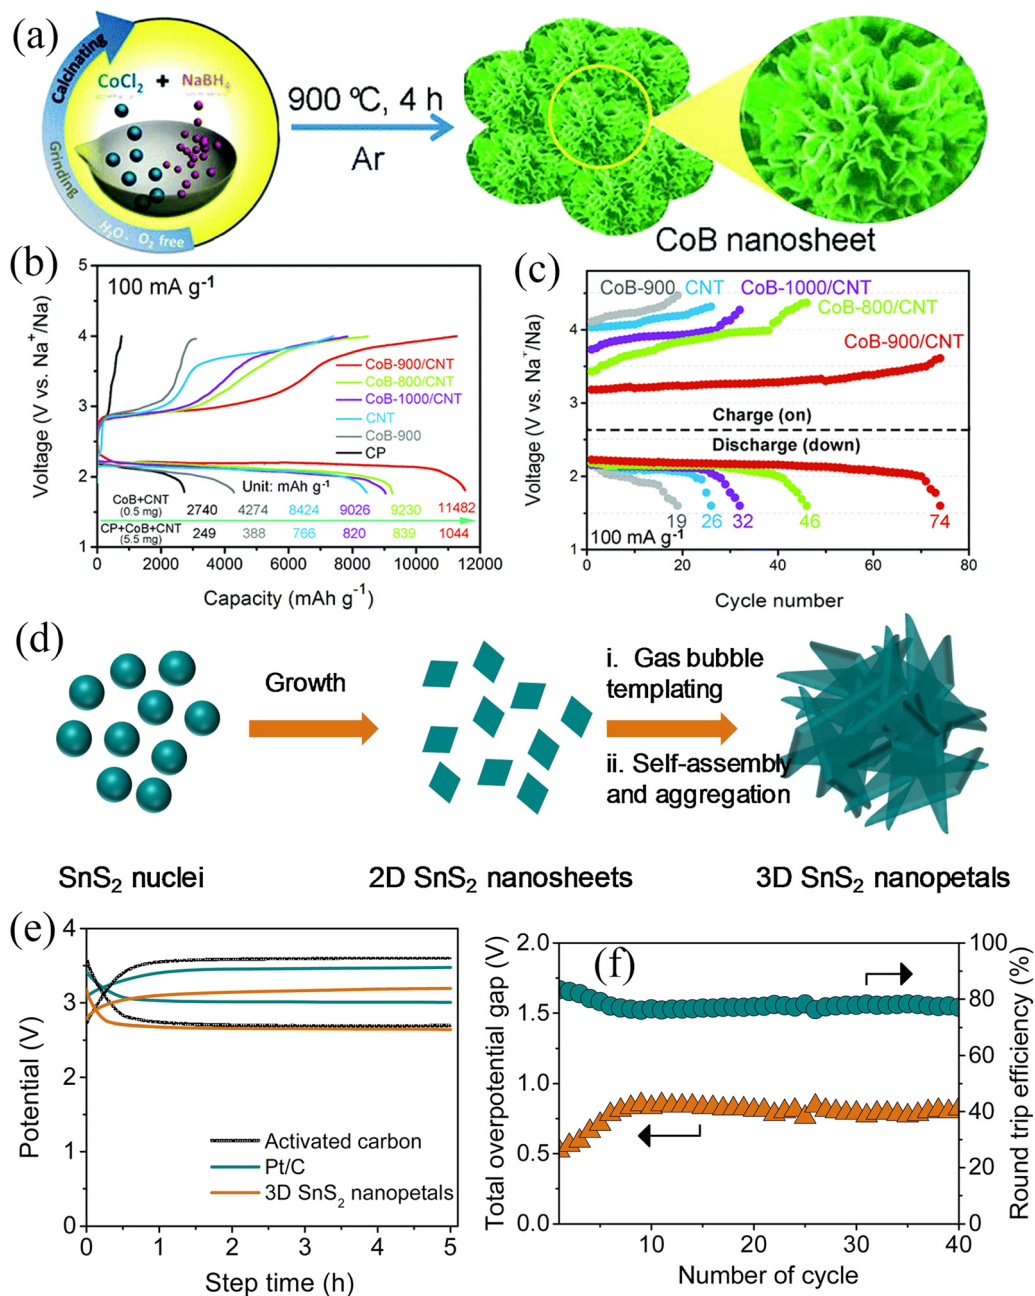


Fig. 8 (a) Schematic illustration of the synthesis of CoB nanosheets. (b) Discharge/charge curves at a current density of 100 mA g^{-1} with different electrodes. (c) The voltage vs. the cycle number at 100 mA g^{-1} with a limited capacity of 2000 mA h g^{-1} for Na- O_2 batteries with different electrodes. (Reproduced from ref. 82 with permission from the Royal Society of Chemistry). (d) Scheme illustration for the growth of 3D SnS_2 nanopetals. (e) Galvanostatic charge/discharge curves of Na- O_2 battery based on 3D SnS_2 nanopetals and comparison with the Pt/C and activated carbon coated on carbon paper as air cathodes at 5.0 mA g^{-1} . (f) Plot of overpotential and round-trip efficiency with cycles. (Reproduced from ref. 83 with permission from the Elsevier).

of only 300 mV at a current density of 5 mA g^{-1} and a maximum power density of 200 mW g^{-1} (Fig. 9d). A well-performing air cathode requires a strongly anisotropic structure which exhibits a large surface-to-volume ratio, continuous electron conduction pathway, and excellent stability to facilitate gas-liquid transport, but it also requires high electrical conductivity to improve electrochemical kinetics. Zhang *et al.*²⁷ fabricated Co-intercalated nitrogen-doped carbon fibers by

electrospinning (Fig. 9e and f). The synergistic effect between nitrogen-doped carbon fibers and metallic Co endowed the composites with high electronic conductivity and catalytic activity. Moreover, the composite material can be directly applied to the air cathode of SABs, avoiding the addition of a binder to reduce the effective mass of active material. The three-dimensional porous structure formed by the interwoven carbon fibers facilitated the transport of matter and electrons.



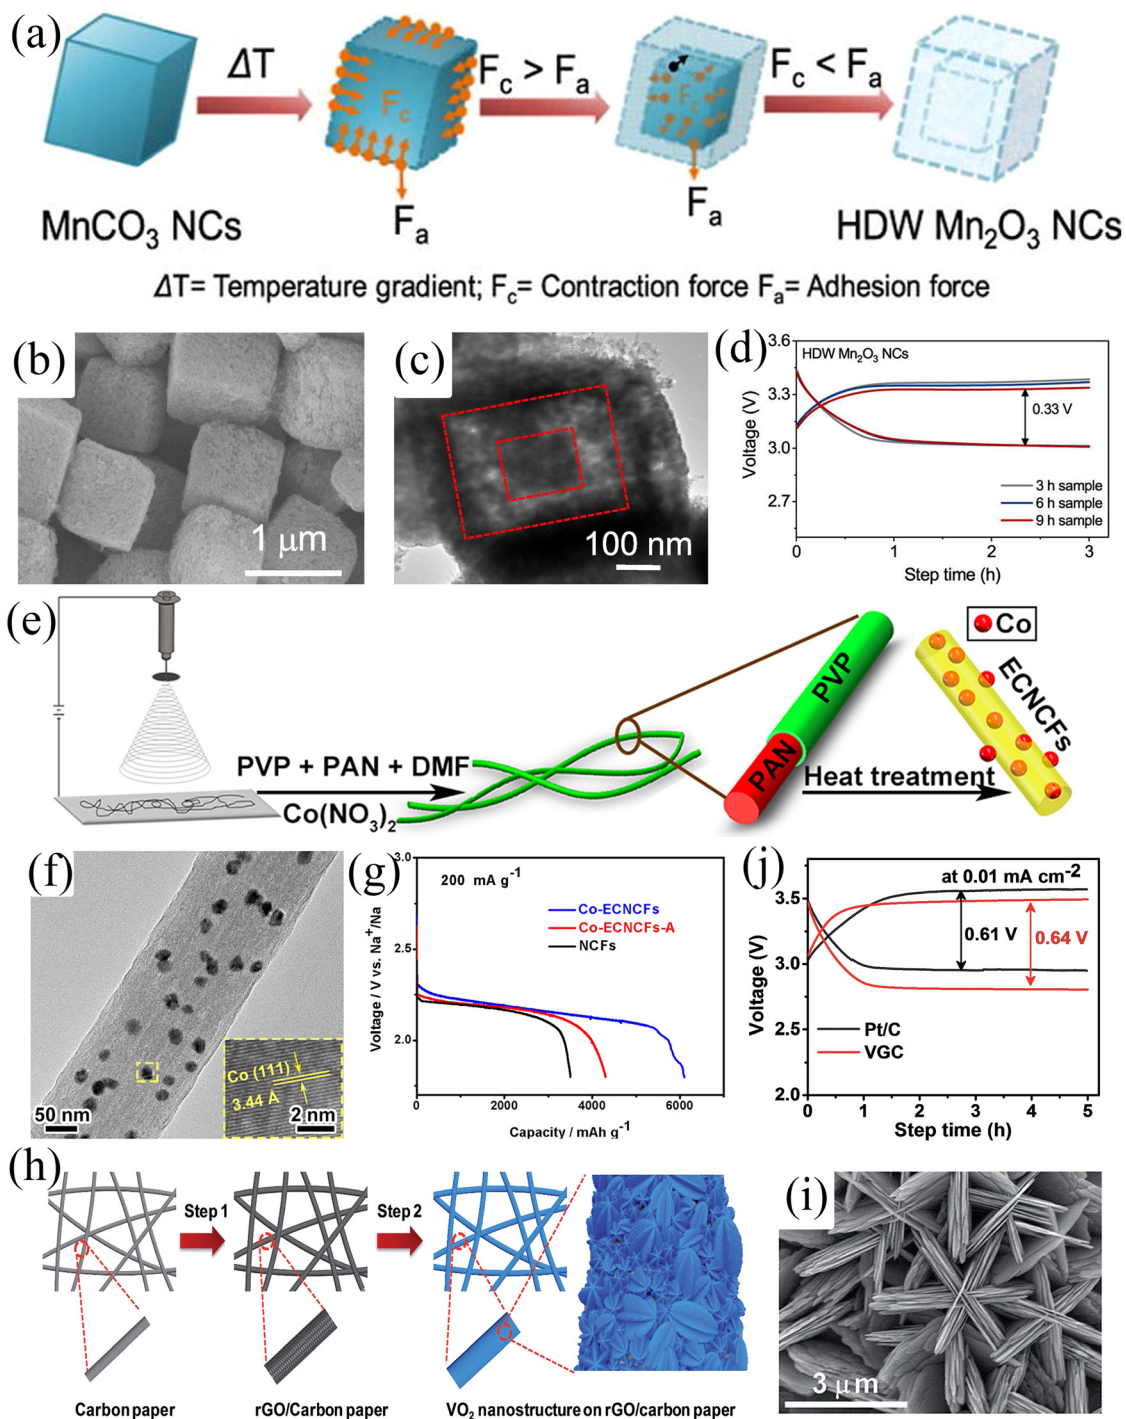


Fig. 9 (a) Schematic illustration of the synthesis of hollow double-walled Mn_2O_3 nanocubes. (b) SEM and (c) TEM images of HDW Mn_2O_3 NCs. (d) Galvanostatic charge/discharge profiles of SABs at a current density of 5.0 mA g^{-1} built-up by Mn_2O_3 electrodes prepared via the hydrothermal method with different time intervals. (Reproduced from ref. 86 with permission from Elsevier). (e) Schematic illustration of the synthesis of Co-ECNCFs. (f) TEM image of Co-ECNCFs (inset: HRTEM image and the (110) lattice plane of Co particles). (g) Galvanostatic discharge curves at a current density of 200 mA g^{-1} with different electrodes. (Reproduced from ref. 27 with permission from Elsevier). (h) Schematic illustration of the synthesis of VGC. (i) SEM image of VGC. (j) The charge–discharge profiles of the assembled SABs using VGC and Pt/C electrodes at a current density of 0.01 mA cm^{-2} . (Reproduced from ref. 88 with permission from the Royal Society of Chemistry).

The outstanding structural features of the composites resulted in the SABs showing excellent electrochemical performance, including high discharge-specific capacity (6102 mA h g^{-1}) by

confining discharge cut-off potential to 1.6 V (Fig. 9g), low charge overpotential (200 mV), and long-cycle stability (112 cycles). Composites with similar structures include VO_2



nanostructures on RGO/carbon paper (VGC)⁸⁸ and atomic layer deposited (ALD) CNT@Co₃O₄.⁸⁴ Fig. 9h shows a schematic diagram of the synthesis of VGC composites.⁸⁸ The composite exhibited a porous hierarchical structure with shortened electrolyte and oxygen diffusion paths (Fig. 9j). The VO₂@rGO/carbon paper composite air cathode exhibited an overpotential of 640 mV and showed good stability over 50 cycles (Fig. 9j).

It is often difficult for one-component TMOs to have excellent ORR and OER activities simultaneously. For example, Co₃O₄ has good ORR activity, but the OER activity is usually not satisfactory, which has a negative effect on the electrochemical performance of the battery.^{89,90} Thus it is highly desirable to design bifunctional catalysts with excellent ORR and OER activities. In 2018, Liu *et al.*¹⁵ obtained CoO/CoP nanosheets with heterostructures by controlling the phosphating degree of Co(CO₃)_{0.5}(OH)0.11H₂O nanosheets (Fig. 10a). This composite exhibited high ORR activity due to the presence of CoO and high OER activity due to the presence of CoP. Furthermore, O-P interpenetration at the interface to form a permeable layer improved the electron transfer, resulting in a simultaneous increase of the ORR and OER activities (Fig. 10b). The Na–O₂ battery with CoO/CoP nanosheets as the air cathode exhibited higher initial specific capacity and longer cycle life (Fig. 10c).

3.3. Noble metal-based materials

Noble metals have excellent electrocatalytic activities and have received extensive attention in metal–air batteries because they can enhance electrocatalytic reaction kinetics by improving the interfacial interactions of reactants.^{96,97} The noble metals used in Na–O₂ batteries mainly include Pt, Pd, Ru, Ag, and Au. Noble metal or noble metal oxides are often dispersed on substrates

with large specific surface areas. For example, RuO₂ has been dispersed on the surface of CNTs,⁶⁶ Pt clusters on defective NiFe layered double hydroxide (LDH) surfaces,⁹⁸ Ru on CNT surfaces,⁹⁹ Ag nanoparticle-modified rGO,¹⁰⁰ and Pd growth on Zn–O.¹⁰¹ Detailed information on noble metal materials and their electrochemical performance is shown in Table 4. Chen *et al.*⁶⁵ synthesized m-RuO₂-B-rGO which exhibited lower overpotential than B-rGO and rGO due to the strong attraction between micron-scale RuO₂ and oxygen, forming an amorphous Na_{2-x}O₂ discharge product, which was identified by Raman spectroscopy (Fig. 11a). The product covered the RuO₂ surface uniformly while avoiding reactions with defect sites to form by-products (Fig. 11b). The Na–O₂ battery with m-RuO₂-B-rGO cathode exhibited an overpotential of 700 mV at 0.05 mA cm⁻² and was stable for more than 100 cycles at the current density of 0.05 mA cm⁻². In addition, Shao and co-workers⁹⁸ electrodeposited Pt clusters on Pt/Ni_xFe-LDHs (Fig. 11c), which exhibited excellent trifunctional catalytic activity (HER/OER/ORR). The excellent electrochemical performance was attributed to: (1) increased electronic conductivity of LDHs, which improved the electrochemical kinetics, (2) the high specific surface area of LDHs, which facilitates the transport of reactants and products, (3) the synergistic effect between Pt clusters and defective LDHs that promoted the adsorption of intermediates in the electrochemical process, and (4) the defects on LDHs that modified the electronic structure of the system, reducing the reaction energy barrier in the electrochemical process and accelerated the reaction kinetics (Fig. 11d). The hybrid Na–air battery based on the Pt/Ni_xFe-LDHs binder-free cathode exhibited an open circuit voltage of 3.01 V, showing a low overpotential of ~660 mV and cycling for over 1000 cycles.

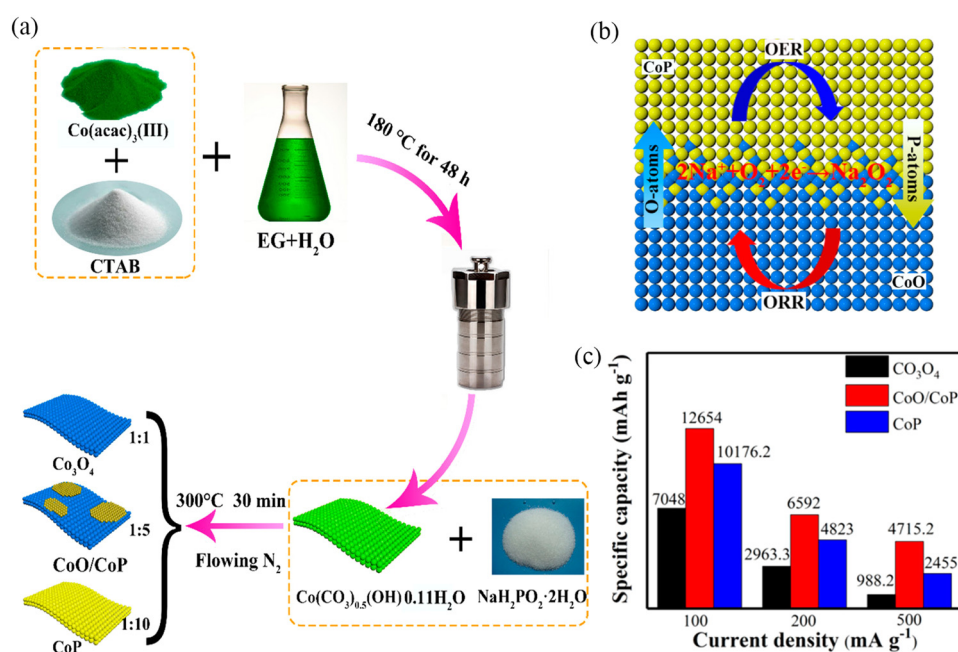


Fig. 10 (a) Synthesis process of Co₃O₄, CoO/CoP and CoP nanosheets. (b) “O–P interpenetration effect” in CoO/CoP heterostructured nanosheet interface. (c) The initial discharge capacity at different current densities with different electrodes. (Reproduced from ref. 15 with permission from the American Chemical Society).



Table 4 Summary of the electrochemical performance of the noble metal-based electrodes used in Na–O₂ batteries

| Cathode | Electrolyte | Current density/ mA g^{-1} | Initial discharge capacity/ mA h g^{-1} | Overpotential/ mV | Discharge product | Ref. |
|--|---|-------------------------------------|--|----------------------------|---|------|
| Pt@GNSs | 1.0 M NaClO ₄ /PC | 0.1 mA cm^{-2} | 7574 | ~1100 | Na ₂ CO ₃ | 102 |
| Ag-RGO | 1.0 M NaPF ₆ /TEGDME | 0.1 mA cm^{-2} | 566 (10th) | 1000–2000 | NaO ₂ , Na ₂ O ₂ , Na ₂ O | 100 |
| Pd/ZnO/C | 0.5 M NaCF ₃ SO ₃ /TEGDME | — | 7.5 mA h cm^{-2} | ~500 | Na ₂ O ₂ 2H ₂ O | 101 |
| Pt/Ni _x Fe LDH | 1.0 M NaClO ₄ /TEGDME//0.1M NaOH | — | 838 | 410 | NaOH | 98 |
| CNT/Ru | 0.5 M NaClO ₄ /DEGDME | 0.191 mA cm^{-2} | — | ~1000 | Na _{2-x} O ₂ | 99 |
| m-RuO ₂ -B-rGO | 0.5 M NaCF ₃ SO ₃ /TEGDME | 0.05 mA cm^{-2} | 3.8 mA h cm^{-2} | ~1000 | Na _{2-x} O ₂ | 65 |
| RuO ₂ /CNT | 0.5 M NaCF ₃ SO ₃ /TEGDME | 100 | 6157 | 370 | NaO ₂ | 66 |
| Ru-SAs@N-rGO | 0.5 M NaCF ₃ SO ₃ /DEGDME | 150 | — | ~900 | Na _{2-x} O ₂ | 18 |
| RuO ₂ /Mn ₂ O ₃ /CNF | 0.5 M NaCF ₃ SO ₃ /TEGDME | 0.05 mA cm^{-2} | 9352 | ~500 | NaO ₂ | 103 |
| Pt ₃ Ni ₁ /Ni _x Fe LDHs | 1.0 M NaClO ₄ /TEGDME | 0.05 mA cm^{-2} | — | ~350 | NaOH | 104 |

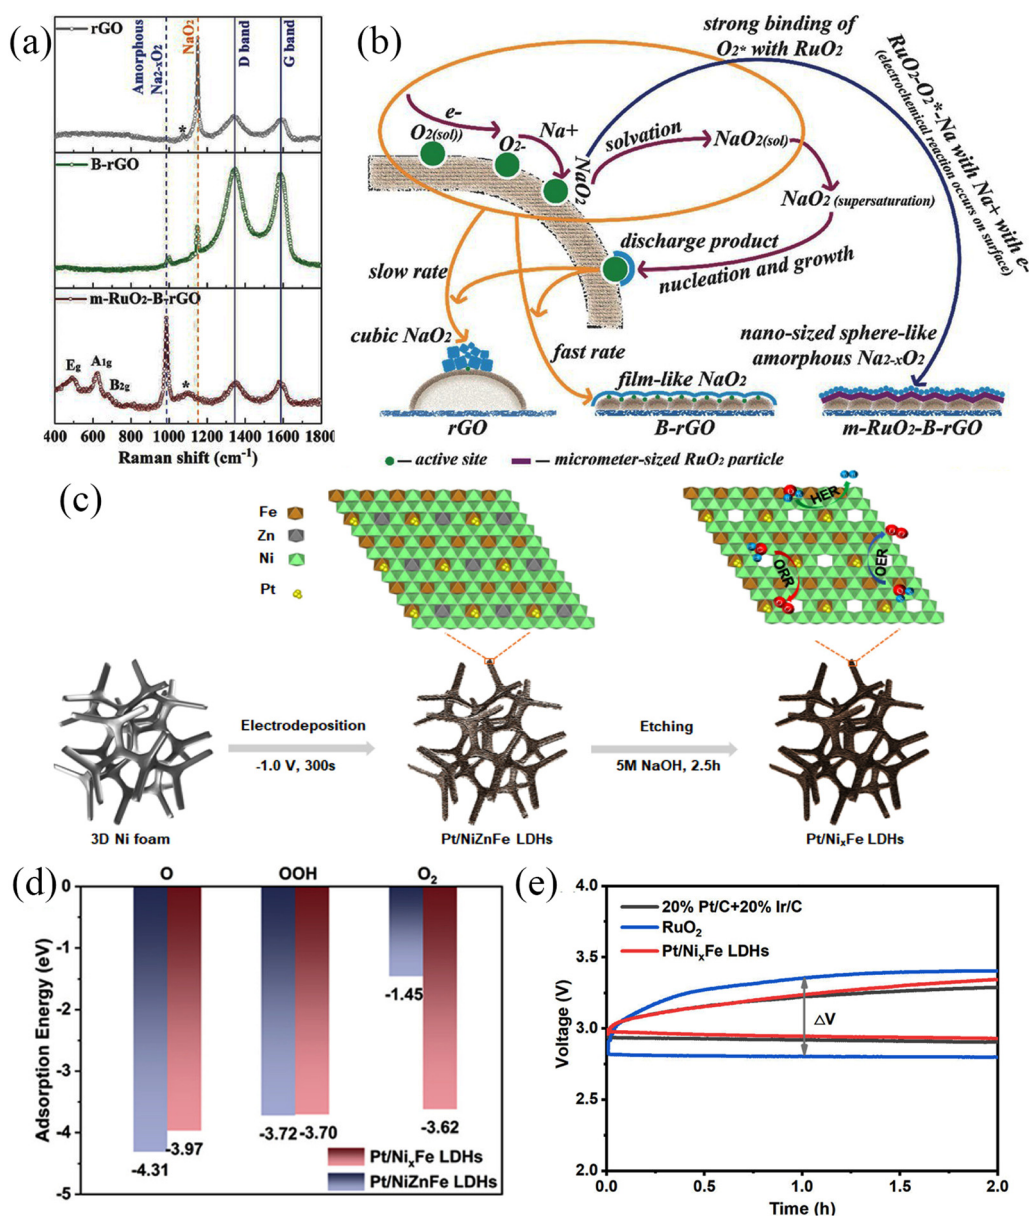


Fig. 11 (a) Raman spectra of rGO, B-rGO, and m-RuO₂-B-rGO electrodes. (b) Schematic illustration of the proposed mechanism for the formation of different morphologies of discharge products on different electrode surfaces. (Reproduced from ref. 65 with permission from Wiley). (c) Schematic illustration of the formation of Pt/Ni_xFe LDHs. (d) Adsorption energies of intermediates on Pt/NiZnFe LDHs and Pt/Ni_xFe LDHs surfaces. (e) The charge–discharge curves of 20% Pt/C + 20% Ir/C, RuO₂ and Pt/Ni_xFe LDHs electrodes. (Reproduced from ref. 98 with permission from the American Chemical Society).



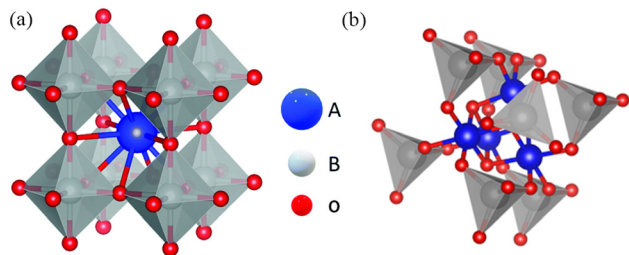


Fig. 12 (a) Crystal structures of a cubic perovskite oxide (ABO_3) (reproduced from ref. 118 with permission from the Royal Society of Chemistry) and (b) a spinel oxide (AB_2O_4).

It yielded a lower overpotential (410 mV) compared to the pure noble metal-based air battery cathode (Fig. 11e), and the stability test results also revealed high stability (1000 cycles). This strategy provides a transformational approach for fabricating high-performance air-battery cathode materials.

3.4. Perovskite (ABO_3) and spinel oxides (AB_2O_4)

Perovskite oxides with physicochemical stability, excellent electronic conductivity, and high redox activity are widely used in the field of catalysis.^{105–109} The general formula of an ideal perovskite oxide compound is ABO_3 (Fig. 12), where A is an alkali metal, lanthanide or alkaline earth metal with 12-fold octahedral ligands. B is a metal with a 3d, 4d or 5d configuration and a 6-fold cubic ligand.¹¹⁰ The ideal perovskite oxide shows a cubic Bravais lattice of space group $Pm\bar{3}m$.¹¹¹ It has been reported that 32 types of A elements and 54 types of B elements can form perovskite structures and these diverse compositions have laid the foundation for expanding their

applications.¹¹² At the same time, spinel oxides have the formula AB_2O_4 , where A occupies the tetrahedral 8a site and B occupies the octahedral 16d site,^{113,114}; these materials show similar physicochemical properties and high redox activity and stability and have been widely used in electrocatalysis.^{115–117}

$Na-O_2$ batteries suffer from slow ORR/OER kinetics and limited material transport. Noble metals such as Pt, Ru, Pd, and Au are often used for the air cathode of $Na-O_2$ batteries to solve the problems of high overpotential and poor cycling stability. However, the high price is not conducive to its large-scale and widespread use. The common binary TMOs discussed previously (such as Co_3O_4 , MnO_2 , Mn_2O_3) exhibit satisfactory electrocatalytic activity as cathode materials. However, ternary metal oxides such as ABO_3 (perovskite)⁶³ and AB_2O_4 (spinel)^{93–95} show better catalytic activity than binary metal oxides. This is due to the coexistence of multiple valences of metal cations causing intervalence charge transfer (IVCT),^{118,119} and/or the formation of oxygen vacancies and structural defects in the system,^{29,120,121} and these play an essential role in improving the catalytic efficiency. Detailed information on perovskite and spinel type materials and their electrochemical performances are summarised in Table 3. In 2015, Chen *et al.*⁶³ synthesized porous $CaMnO_3$ microspheres as air cathodes for $Na-O_2$ batteries (Fig. 13a). The porous micro-nano structures provided abundant redox sites and exhibited remarkable electrocatalytic activity. Moreover, the size of the microspheres can be tailored by varying experimental conditions, such as the amount of carbonate precipitant and reaction temperature. The porous structure of $CaMnO_3$ provides a high specific discharge capacity of 9560 mA h g^{-1} at a current density of 100 mA g^{-1} (Fig. 13b), and these can be steadily cycled for 80 cycles at a

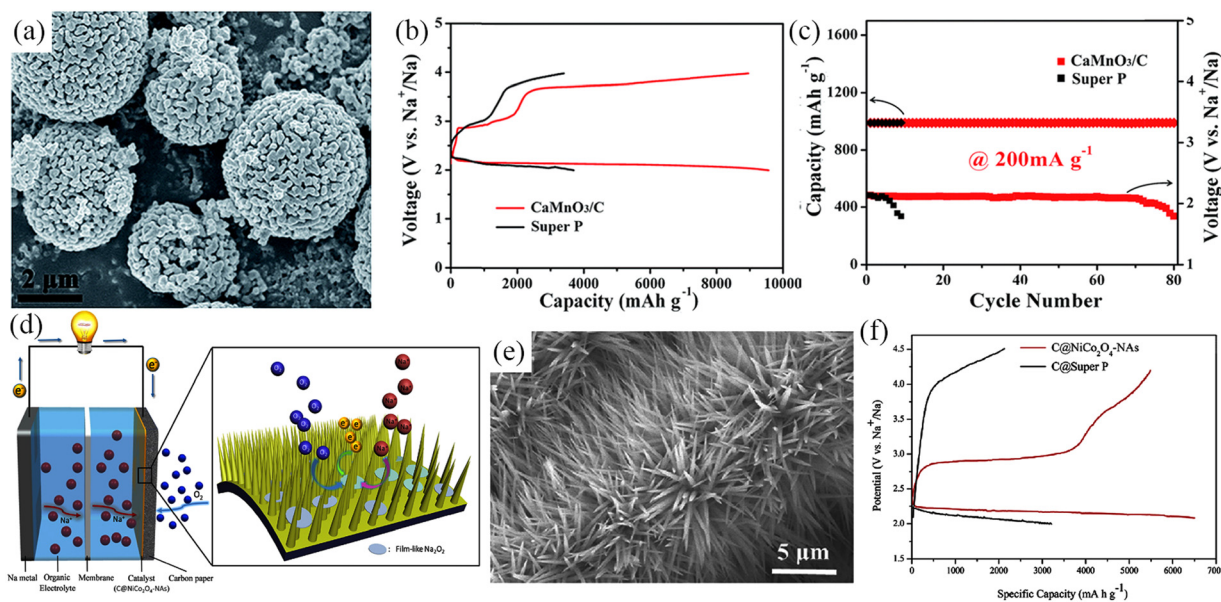


Fig. 13 (a) SEM image of $CaMnO_3$ nanoparticles. Discharge–charge curves (b) and cycling performance (c) of $CaMnO_3/C$ and Super P electrodes in $Na-O_2$ batteries. (Reproduced from ref. 63 with permission from the Royal Society of Chemistry). (d) Schematic illustration of the $Na-O_2$ batteries structure with $C@NiCo_2O_4-NAs$ based cathode. (e) SEM image of $C@NiCo_2O_4-NAs$. (f) Initial charge–discharge curves of $C@Super P$ and $C@NiCo_2O_4-NAs$ electrode at 50 mA g^{-1} . (Reproduced from ref. 95 with permission from Elsevier).



current density of 200 mA g⁻¹ with the cut-off capacity of 1000 mA h g⁻¹ (Fig. 13c).

Currently, cobalt metal-containing ternary transition oxides have attracted tremendous attention as electrocatalysts with high OER/ORR activity.^{122–125} During the cathode assembly, typically, a polymeric binder is required to maximize the physical contact between the active material and the current collector. However, this may result in a significant increase in the contact resistance and thereby reduce the battery performance. Further, the polymeric binder can undergo decomposition and cause side reactions.¹²⁶ Fu *et al.*⁹³ prepared a binder-free and carbon-free NiCo₂O₄/Ni foam composite air cathode, which provided an initial discharge-specific capacity of 1762 mA h g⁻¹ at a current density of 20 mA g⁻¹. However, TMOs generally lack sufficient electronic conductivity, cycling stability, and exposed surface area. Liu *et al.*⁹⁵ fabricated sea urchin-like C@NiCo₂O₄ nanoneedles (C@NiCo₂O₄-NAs) *in situ* grown on carbon paper by a hydrothermal method and directly applied them to the air cathode of Na–O₂ batteries (Fig. 13d and e). The C@NiCo₂O₄-NAs exhibited high specific surface area and low contact resistance, exposing a large number of catalytically active sites. Then, the C@NiCo₂O₄-NAs cathode released a high initial discharge specific capacity of 6500 mA h g⁻¹ at current density of 50 mA g⁻¹ (Fig. 13f) and showed high stability of 120 cycles. Further, the multi-layered structure produced was observed to be favorable for material transport and accommodating discharge products. Thin-film Na₂O₂ discharge products are formed on the nanoneedle surfaces and gaps and this unique structure facilitates decomposition of discharge products during subsequent charging, exhibiting a low overpotential of 600 mV.

Perovskite oxides with porous structures can enable adequate control of the composition and incorporation of functional materials, which are crucial for improving the catalytic activity, stability, and mass transport of catalysts. The catalyst morphology is also significant in improving the battery performance.¹¹⁸ First, the porous structure increases the contact area between the active material and the electrolyte and improves the ion storage capacity, while the porous structure promotes electron and ion transport. Second, the porous structure is conducive to material exchange, prevents the agglomeration of discharge products, and is beneficial for the electrode maintaining stability during cycling, achievement of long-term stability and prolongment of the cycle life. Third, electrodes with porous structures can help to optimize the interfacial interactions between air electrodes, discharge products, and electrolytes. In addition, introducing defects in the perovskite oxide is one of the most popular methods to improve catalytic performance, as this can allow for the modification of the crystal structure and improve the electronic conductivity and redox site density to prepare low-cost, catalytically efficient perovskite electrocatalysts. A-site cation substitution is a well-established approach to enhance the electrocatalytic activity and has been shown to improve the battery's power, energy density, and cycle life by increasing the electrical conductivity and reducing the cathode overpotential. Defects created by

A-site cation substitution affect electrocatalytic performance in several ways, such as creating charge-compensated oxygen vacancies,^{127–131} generating charge-compensated B-site cation vacancies,¹²⁸ and reducing the activation energy for cation, oxygen, or vacancy diffusion.¹¹² Cerium-doped (La_{1-x}Ce_x)MnO₃ ($x = 0, 0.05, 0.1$ and 0.15) chalcogenide oxides were prepared by Guo *et al.*¹³² using the sol-gel method. Ce replacement of La can effectively improve the ORR activity of perovskite due to the increase in the proportion of Mn⁴⁺ during the replacement process (Fig. 14a and b), which is beneficial for exchange of O₂²⁻/OH⁻, thereby improving the ORR performance. The B-site is usually considered the redox-active site for the OER/ORR reaction.¹³³ The substitution of B-site cation can also be used to enhance the electrocatalytic activity of perovskite oxides. Cu/Co-doped LaMn_{0.8}M_{0.2}O₃ (M = Cu, Co) perovskite oxides were synthesized by Hu *et al.*¹³⁴ (Fig. 14c). The substitution of low-valent cations at the B-site increased the oxygen vacancy concentration and Mn⁴⁺ content, both of which favoured the ORR process. While Mn⁴⁺ has a more vital ability to accept electrons than Mn³⁺, the excess Mn⁴⁺ in the system promotes O₂ evolution, which will improve the OER performance (Fig. 14d).

The formation of anion vacancies in perovskite oxides is another strategy to tailor the functionality of materials for OER/ORR. For instance, oxygen vacancies in the defective perovskite oxides (ABO_{3-δ}) showed an enhancement in the oxygen ion mobility.¹¹² Typically, there are two main approaches for the creation of oxygen vacancies: (1) cation substitution-induced oxygen vacancies and (2) elemental non-chemical stoichiometry-induced oxygen vacancies.¹¹² The partial introduction of donor dopants in the A-sites is the most common method to generate oxygen vacancies and this has been shown to enhance the electrocatalytic activity (Fig. 14e). These defects are created based on the charge compensation mechanism.^{112,118} The oxygen vacancies can be formed when the perovskite oxide is heated under a reducing atmosphere. Nonetheless, these vacancies have been observed to be unstable with prolonged exposure to air. Another strategy to create oxygen vacancies involves the formation of A-site vacancies. For example, Shao's group¹³⁵ prepared La_{1-x}FeO_{3-δ} ($x = 0.02, 0.05, 0.1$) OER/ORR bifunctional electrocatalysts with the absence of A-site cations (Fig. 14f). The OER/ORR performance of La_{1-x}FeO_{3-δ} was significantly improved compared to the untreated samples with La_{0.95}FeO_{3-δ} showing the best OER and ORR activities. The XPS results (Fig. 14g) can be analyzed to obtain La_{1-x}FeO_{3-δ} perovskite oxides with A-site cation deficiency that have surface oxygen vacancies (O₂²⁻/O⁻), and the OER/ORR reactions occur on the surface of perovskite oxides with the surface oxygen vacancies enhancing the OER and ORR reactions. The XPS and Mössbauer spectra of La_{1-x}FeO_{3-δ} (Fig. 14g and h) showed the presence of high chemical valence iron (Fe⁴⁺) in the treated samples and the presence of Fe³⁺/Fe⁴⁺ redox couple enhanced the electrocatalytic performance of La_{1-x}FeO_{3-δ}.

The defect engineering (A-site substitution/absence, B-site substitution/absence, anion absence) of perovskite oxides leads



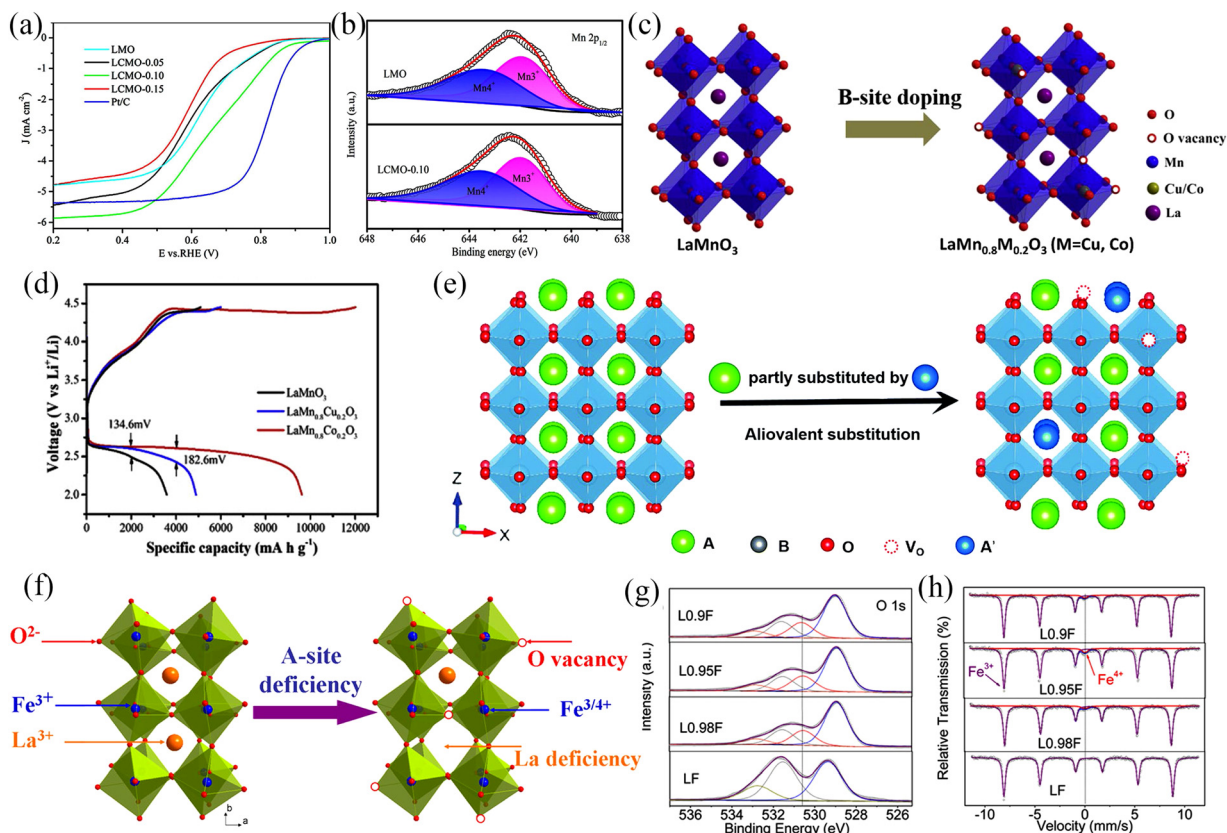


Fig. 14 (a) Linear-sweep voltammetry curves at 1600 rpm with different samples. (b) XPS spectra of Mn 2p of prepared samples. (Reproduced from ref. 132 with permission from the American Chemical Society). (c) Structure of LaMnO_3 , $\text{La}(\text{Mn}_{0.8}\text{M}_{0.2})\text{O}_3$ ($\text{M} = \text{Cu}, \text{Co}$). (d) Initial charge–discharge profiles of LaMnO_3 and $\text{La}(\text{Mn}_{0.8}\text{M}_{0.2})\text{O}_3$ ($\text{M} = \text{Cu}, \text{Co}$) at 500 mA g^{-1} . (Reproduced from ref. 134 with permission from Elsevier). (e) Schematic illustration of the formation of oxygen vacancies due to A-site substitution. (Reproduced from ref. 112 with permission from the Royal Society of Chemistry). (f) Schematic illustration of the formation of Fe^{4+} and oxygen vacancies in A-site-substitution $\text{La}_{1-x}\text{FeO}_{3-\delta}$. (g) XPS spectra of O 1s and (h) Mössbauer spectra of LaFeO_3 , $\text{La}_{0.98}\text{FeO}_{3-\delta}$, $\text{La}_{0.95}\text{FeO}_{3-\delta}$, and $\text{La}_{0.9}\text{FeO}_{3-\delta}$ samples. (Reproduced from ref. 135 with permission from the American Chemical Society).

to a significant improvement in OER and ORR catalytic activities of perovskite oxides, which is beneficial for increased applicability in electrocatalysis, fuel cells, and metal–air batteries. A summary of approaches that have been used to create defects in perovskite electrocatalysts and their applications for ORR/OER or metal–air batteries are summarised in Table 5.

3.5. Metal–organic frameworks and their derivatives

Metal–organic frameworks (MOFs) are obtained by the reaction of metallic complexes and organic linkers in a specific environment. The coordination reaction between metal nodes and organic ligands results in a porous network structure and endows MOFs with a large specific surface area, which is conducive to material contact, transport and exchange and ensures the continuation of chemical reactions.^{145–147} The abundant pores, diverse crystal structures, and outstanding redox activity in MOFs make them widely applicable for energy conversion.¹⁴⁸ In particular, the application of MOFs and their derivatives in bifunctional catalysts (OER/ORR) and their extension (metal–air batteries) provides a natural advantage (Fig. 15a).¹⁴⁹ Metal–air batteries involve gas transport and material conversion during the charge/discharge process and

MOFs with porous crystal structures can be designed to meet application requirements. Combining MOFs with other electrocatalysts with excellent OER/ORR activity is also possible, which can exhibit even better electrochemical performance. In addition, using MOFs as precursors for MOF-based derivatives can help preserve the basic framework of MOFs to obtain a hierarchical porous structure, which facilitates the electrochemical mass transfer process. The choice of metal nodes and organic linkers is also significant for OER/ORR activity. The metal cation species and valence states affect the organic ligands' spatial arrangement to form MOFs with different electrochemical properties. Guo *et al.*¹⁵⁰ synthesized a series of 2D metal–organic frameworks $\text{M}_3(\text{C}_6\text{S}_6)_2$ ($\text{M} = \text{V}, \text{Cr}, \text{Mn}, \text{Fe}, \text{Co}, \text{Nb}, \text{Mo}, \text{Tc}, \text{Ru}, \text{Rh}, \text{Pd}, \text{Ir}, \text{and Pt}$) with different metal centres (Fig. 15b). $\text{M}_3(\text{C}_6\text{S}_6)_2$ exhibited different catalytic activities (Fig. 15c) owing to the presence of metal nodes with different numbers of simple d-electrons. The OER and ORR overpotentials of $\text{Rh}_3(\text{C}_6\text{S}_6)_2$ were 430 and 420 mV, respectively, showing the best bifunctional catalytic activity. The organic ligands enable the metal cation active sites to be uniformly distributed in the MOF framework. During the preparation of MOF-derived carbon materials, the ligand bonds in the system break and the



Table 5 Summary of use of defective perovskites as electrocatalysis in various applications

| Perovskites | Dopant and defect type | Method | Application | Ref. |
|--|---|---|---------------------------|------|
| $\text{La}_{0.9}\text{CoO}_{3-\delta}$ | La and O vacancies ($\text{O}_2^{2-}/\text{O}^-$: 56.2%) | Polymer-assisted (A-site cation deficiency) | ORR/OER | 127 |
| $(\text{La}_{0.8}\text{Sr}_{0.2})_{1.05}\text{MnO}_3$ | Mn and O vacancies ($\text{O}_2^{2-}/\text{O}^-$: 32.1%; Mn^{3+} : 32.8%) | Polymer-assisted (A-site cation excessive) | ORR/OER | 128 |
| $\text{Pr}(\text{Ba}_{0.5}\text{Sr}_{0.5})(\text{Co}_{1.9}\text{Ni}_{0.1})\text{O}_{5+\delta}$ | Ni dopant ($\text{O}_{\text{ads}}/\text{O}_{\text{lat}}$: 2.48) | Pechini method (elemental doping) | Zn-air battery | 136 |
| $\text{La}_{0.3}(\text{Ba}_{0.5}\text{Sr}_{0.5})_{0.7}\text{Co}_{0.8}\text{Fe}_{0.2}\text{O}_{3-\delta}$ | La dopant and O vacancies | Polymerized complex method (elemental doping) | ORR/OER | 137 |
| $\text{La}(\text{Ni}_x\text{M}_{1-x})\text{O}_3$ (M = Co, Mn, Fe) | Ni dopant | Sol-gel method (elemental doping) | ORR/OER | 138 |
| $\text{BaBi}_{0.05}\text{Co}_{0.85}\text{Nb}_{0.1}\text{O}_{3-\delta}$ | Nb dopant and O vacancies ($\text{O}_{\text{ads}}/\text{O}_{\text{lat}}$: 1.85) | Solid state reaction (elemental doping) | ORR/OER | 139 |
| $5.84\% \text{ S-LaMO}_3$ (M = Co, Fe, Ni) | S dopant (O: 71.7%) | Sol-gel method and anneal (elemental doping) | Zn-air battery | 140 |
| P-doped $\text{LaFeO}_{3-\delta}$ | P dopant and O vacancies ($\text{O}_2^{2-}/\text{O}^-$: 30.6%) | Sol-gel method and anneal (elemental doping) | ORR/OER | 141 |
| $\text{Sr}_{0.95}\text{Nb}_{0.1}\text{Co}_{0.8}\text{Ni}_{0.1}\text{O}_{3-\delta}$ | O vacancies ($\text{O}_2^{2-}/\text{O}^-$: 7.18%) | Heat treatment in H_2/Ar | ORR/OER/HER | 142 |
| $(\text{La}_{1-x}\text{Ce}_x)\text{MnO}_3$ | Ce dopant | Sol-gel method (elemental doping) | Zn-air battery | 132 |
| $(\text{Pr}_{0.5}\text{Ba}_{0.5})\text{CoO}_{3-\delta}$ | Element dopant | Sol-gel method (elemental doping) | Zn-air battery | 143 |
| $\text{La}(\text{Mn}_{0.8}\text{Co}_{0.2})\text{O}_3$ | Element dopant ($\text{Mn}^{4+}/\text{Mn}^{3+}$: 0.55) | Gel-combustion | Li-O ₂ battery | 134 |
| $(\text{La}_{0.8}\text{Sr}_{0.2})(\text{Co}_{0.8}\text{Ni}_{0.2})\text{O}_{3-\delta}$ | Element dopant and O vacancies ($\text{O}^-/\text{O}_2^{2-}$: 5.94% $\text{OH}^-/\text{CO}_3^{2-}$: 53.64%) | Sol-gel method (elemental doping) | Li-O ₂ battery | 144 |

metal centres are dispersed throughout the carbon skeleton. Ma's team¹⁵¹ used a stepwise self-assembly method to load Ni and Fe single atoms on the inner and outer walls of hollow carbon spheres, respectively (Fig. 15d), resulting in composites with good bifunctional catalytic activity. Both experimental and theoretical calculations demonstrate the excellent ORR activity of the inner wall Fe-N₄ cluster (Fig. 15e), as judged by a high half-wave potential of 0.83 V. The outer Ni-N₄ cluster exhibits excellent OER electrocatalytic activity, which delivered a low overpotential of 400 mV (Fig. 15f). In summary, both pristine MOFs and the MOF derivatives show excellent bifunctional catalytic activity and have outstanding application prospects in Na-O₂ batteries. Detailed information on metal-organic frameworks, their derivatives, and their electrochemical performance is provided in Table 6.

Hui *et al.*¹⁵² proposed a post-oxidation strategy for the insufficient OER activity of Co-PBA and prepared defective Prussian blue analogues with exposed Co(III) active sites and Fe(CN)₆ vacancies (D-Co-PBA) (Fig. 16a). Theoretical calculations demonstrated that Fe(CN)₆ vacancies modulate the electronic structure of the entire D-Co-PBA to lower the reaction energy barrier of the decisive step in the OER process and improve the reaction kinetics of the OER process. The D-Co-PBA catalyst showed an overpotential of only 400 mV at a current density of 10 mA cm⁻² (Fig. 16b). The D-Co-PBA(OER)-Pt/C(ORR) bifunctional catalyst was used as the air cathode electrode of a hybrid Na-O₂ battery. The bifunctional air cathode exhibited a very low overpotential of 150 mV at a current density of 0.01 mA cm⁻², which is lower than the overpotential of the Ir/C(OER)-Pt/C(ORR) bifunctional cathode (Fig. 16c).

In addition to the direct use of MOFs as air cathodes for Na-O₂ batteries, MOF-based derivatives can also be prepared for use in air cathodes for Na-O₂ batteries. In 2019, Sun *et al.*¹⁵³

prepared MOF-NCNFs using ZIF-67 as a precursor (Fig. 16d). Under reducing atmosphere (Ar/H₂) at 700 °C, the ZIF-67 precursors were pyrolyzed and converted into a robust framework structure. The synergistic effect of the nitrogen-doped carbon framework containing Co nanoparticles in the framework structure induces more oxygen adsorption and electrocatalytically active sites to promote electron transfer in OER and ORR processes. At the same time, the stable porous carbon skeleton facilitates the smooth mass transfer process and contributes to the stability of the catalyst during the charging and discharging process for a hybrid Na-O₂ battery. MOF-NCNFs exhibited an overpotential of 300 mV at a current density of 0.01 mA cm⁻², which was superior to commercial RuO₂ (500 mV), Pt/C (500 mV), Co-CNTs (670 mV), NCNTs (770 mV), multi-walled carbon nanotubes (MWNTs) (900 mV) and carbon paper (1180 mV), and could be stably cycled for more than 35 cycles (Fig. 16e and f). Subsequently, Xue *et al.*¹⁵⁴ synthesized highly dispersed Co nanoparticle-modified N-doped defect carbon framework (Co-N-C) using ZnCo bimetal-organic framework as a precursor for hybrid Na-O₂ battery (Fig. 16g). Nitrogen-doped defective carbon, CoN_x, and Co nanoparticles in Co-N-C can serve as OER and ORR active sites, while Co-N-C species connect carbon materials with Co particles and facilitate interfacial electron transfer (Fig. 16h). The Co-N-C-0.5 anode with a high number of active sites, strong internal synergy, and significantly enhanced electron transfer capacity exhibited only an overpotential of 310 mV along with a 90.0% round-trip efficiency at a current density of 0.1 mA cm⁻² (Fig. 16i). In addition to monometallic derivatives, bimetallic derivative electrocatalysts have been prepared. Hui *et al.*¹⁵⁵ prepared bimetallic nanoparticles encapsulated in nitrogen-doped carbon (Co-Fe@NC) for hybrid Na-air batteries and the Co-Fe@NC air cathode exhibited lower overpotential (270 mV) and long cycle life (700 h) in comparison to



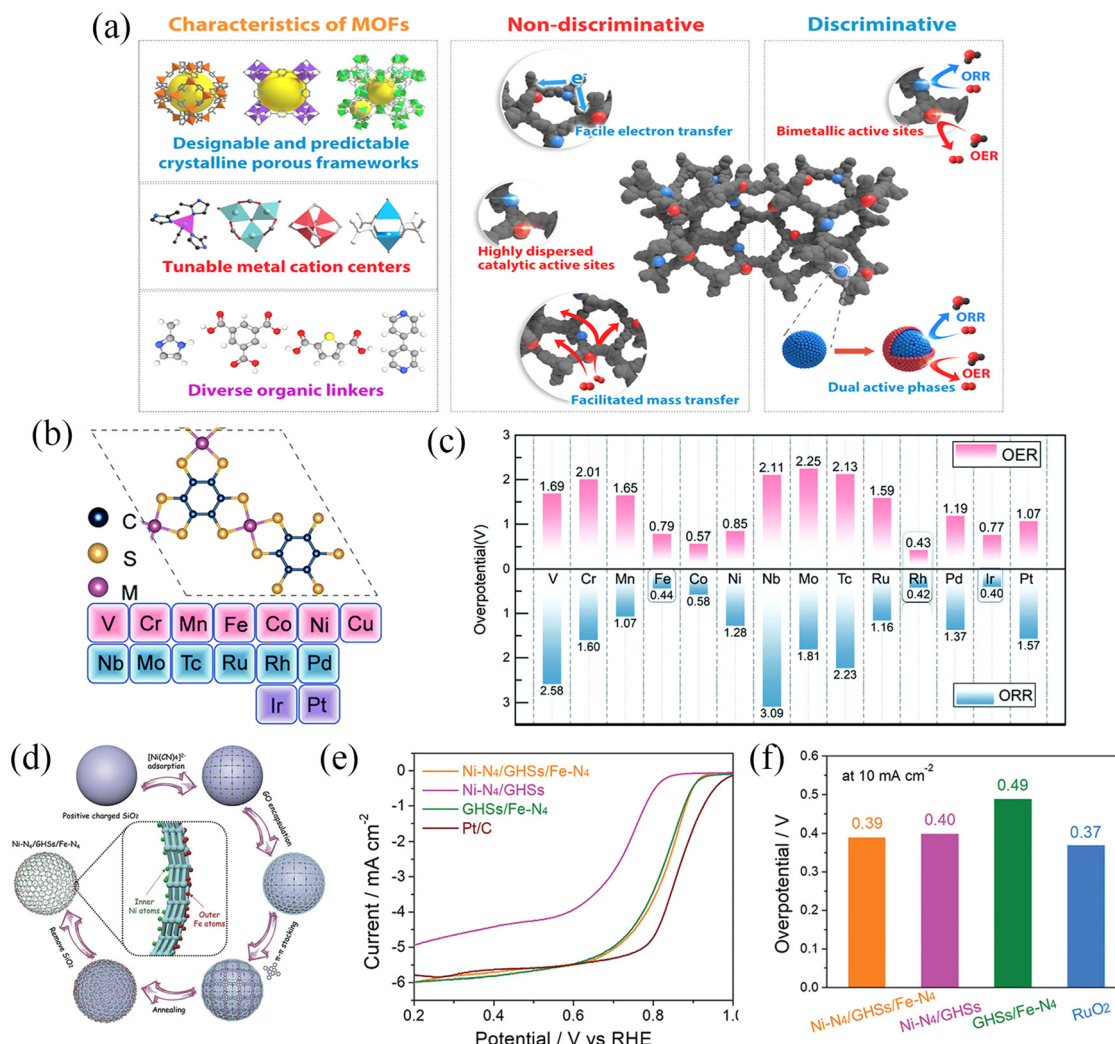


Fig. 15 (a) Schematic illustration of the outstanding features of MOFs and their derivatives in OER and ORR application. (Reproduced from ref. 148 with permission from Elsevier). (b) Schematic illustration of $M_3(C_6S_6)_2$ with different transition metals. (c) OER and ORR overpotentials of $M_3(C_6S_6)_2$. (Reproduced from ref. 150 with permission from the Royal Society of Chemistry). (d) Synthesis procedure for the Ni-N₄/GHSs/Fe-N₄ catalyst. (e) The ORR results and (f) the OER results of different catalysts. (Reproduced from ref. 151 with permission from Wiley).

the Pt/C + RuO₂ electrode (overpotential increased to 1330 mV after 400 h).

Many studies also used MOFs as precursors to prepare metal oxides¹⁵⁶ and metal phosphides.¹⁷ Liu *et al.*¹⁵⁶ synthesized the hierarchical Co₃O₄@MnCo₂O_{4.5} nanocubes (h-Co₃O₄@MnCo₂O_{4.5} NCs) with a core-shell structure using cubic ZIF-67 precursor (Fig. 17a–c). The abundant pores in h-Co₃O₄@MnCo₂O_{4.5} NCs facilitated the transport and exchange of substances during the recycling process and significantly enhanced the electrocatalytic activity. The Na–O₂ batteries based on h-Co₃O₄@MnCo₂O_{4.5} NCs cathode exhibited a high specific discharge capacity of 8400 mA h g⁻¹ (Fig. 17d) and showed high structural stability after 135 cycles. Further, Hui *et al.*¹⁷ synthesized three-dimensionally-structured Fe-doped NiCoP (Fe-NiCoP) on nickel foam (Fig. 17e and f) and used it as a bifunctional air cathode for Na–O₂ batteries. Fe-doping significantly improved the electrocatalytic performance of

NiCoP, while carbon coating (Fe-NiCoP@C) facilitated the enhancement of catalytic performance and stability. The linear cyclic voltammetry (LSV) curves of different electrodes are shown in Fig. 17g. Compared to NiCoP (0.64 V) and Fe-NiCoP (0.80 V), Fe-NiCoP@C showed a maximum onset potential of 0.81 V. In addition, Fe-NiCoP and Fe-NiCoP@C showed higher limit current densities and better ORR performance than NiCoP. Meanwhile, Fe-NiCoP@C exhibited an overpotential of 270 mV at a current density of 10 mA cm⁻² (Fig. 17h), which is lower than reported for most OER catalysts. First-principles calculations (DFT) revealed the origin of the high catalytic activity of Fe-NiCoP@C. Fig. 17i and j presents the Gibbs free energies (ΔG) of the relevant intermediates in the ORR/OER process for two samples (Fe-NiCoP and NiCoP). In the ORR process, the formation of OH⁻ is a rate-determining step. It was shown that the presence of Fe in Fe-NiCoP, compared to NiCoP, considerably increased the adsorption strength of the



Table 6 Summary of the electrochemical performance of the metal–organic frameworks and their derivatives and other cathode electrodes used in Na–O₂ batteries

| Cathode | Electrolyte | Current density/ mA cm^{-2} | Overpotential/ mV | Discharge product | Ref. |
|---|--|--------------------------------------|----------------------------|--|------|
| D-Co-PBA + Pt/C | Cathode: 0.1 M NaOH | 0.01 | 150 | NaOH | 152 |
| MOF-NCNTs-N ₂ -4 | 1.0 M NaClO ₄ in EC/DMC (1:1) with 1 vol% FEC//1.0 M NaOH | 0.1 | 350 | NaOH | 157 |
| MOF-NCNTs | 1.0 M NaClO ₄ in EC/DMC (1:1) with 1 vol% FEC//1.0 M NaOH | 0.1 | ~200 | NaOH | 153 |
| Co–N–C-0.5 | 1.0 M NaClO ₄ in EC/DMC (1:1) with 1 vol% FEC//1.0 M NaOH | 0.1 | 310 | NaOH | 154 |
| Co–Fe@NC | 1.0 M NaClO ₄ in EC/DMC/EMC (1:1:1) with 5 vol% FEC//1.0 M NaOH | 0.1 | ~205 | NaOH | 155 |
| Fe–N ₄ /CNT | 1.0 M NaCF ₃ SO ₃ /TEGDME//0.1 M NaOH | — | — | NaOH | 158 |
| Fe–NiCoP@C | Cathode: 0.1 M NaOH | 0.01 | 140 | NaOH | 17 |
| h- | 1.0 M NaClO ₄ /TEGDME | 50 mA g^{-1} | 450 | Na ₂ O ₂ | 156 |
| Co ₃ O ₄ @MnCo ₂ O _{4.5} | | | | Na _{2-x} O ₂ | |
| Bi ₂ Ru ₂ O ₇ | 1.0 M NaCF ₃ SO ₃ /TEGDME//0.1 M NaOH | 0.01 | ~210 | NaOH | 26 |
| La ₂ Co ₂ O ₇ | 0.5 M NaCF ₃ SO ₃ /TEGDME | 100 mA g^{-1} | ~500 | Na ₂ O ₂ , Na ₂ O | 159 |
| Tl ₂ Rh ₂ O ₇ | 1.0 M NaCF ₃ SO ₃ /TEGDME | 0.01 | ~500 | NaOH | 160 |
| P-Bi ₂ Rh ₂ O _{6,8} | 1.0 M NaCF ₃ SO ₃ /TEGDME//0.1 M NaOH | 0.01 | ~170 | NaOH | 161 |
| P-Tl ₂ Ru ₂ O ₇ | 1.0 M NaCF ₃ SO ₃ /TEGDME | 0.01 | ~160 | NaOH | 162 |
| Na ₂ CoPO ₄ F | 1.0 M NaClO ₄ in PC//0.1 M NaOH | 0.01 | 417 | NaOH | 163 |
| Ni _{1.5} Co _{1.5} (PO ₄) ₂ | 1.0 M NaClO ₄ in PC//0.1 M NaOH | 0.01 | ~750 | NaOH | 164 |
| Co ₃ (PO ₄) ₂ | 1.0 M NaCF ₃ SO ₃ /TEGDME//0.1 M NaOH | 0.01 | 230 | NaOH | 165 |
| K ₂ Co(PO ₃) ₄ | 1.0 M NaClO ₄ in PC//0.1 M NaOH | 0.02 | ~500 | NaOH | 16 |

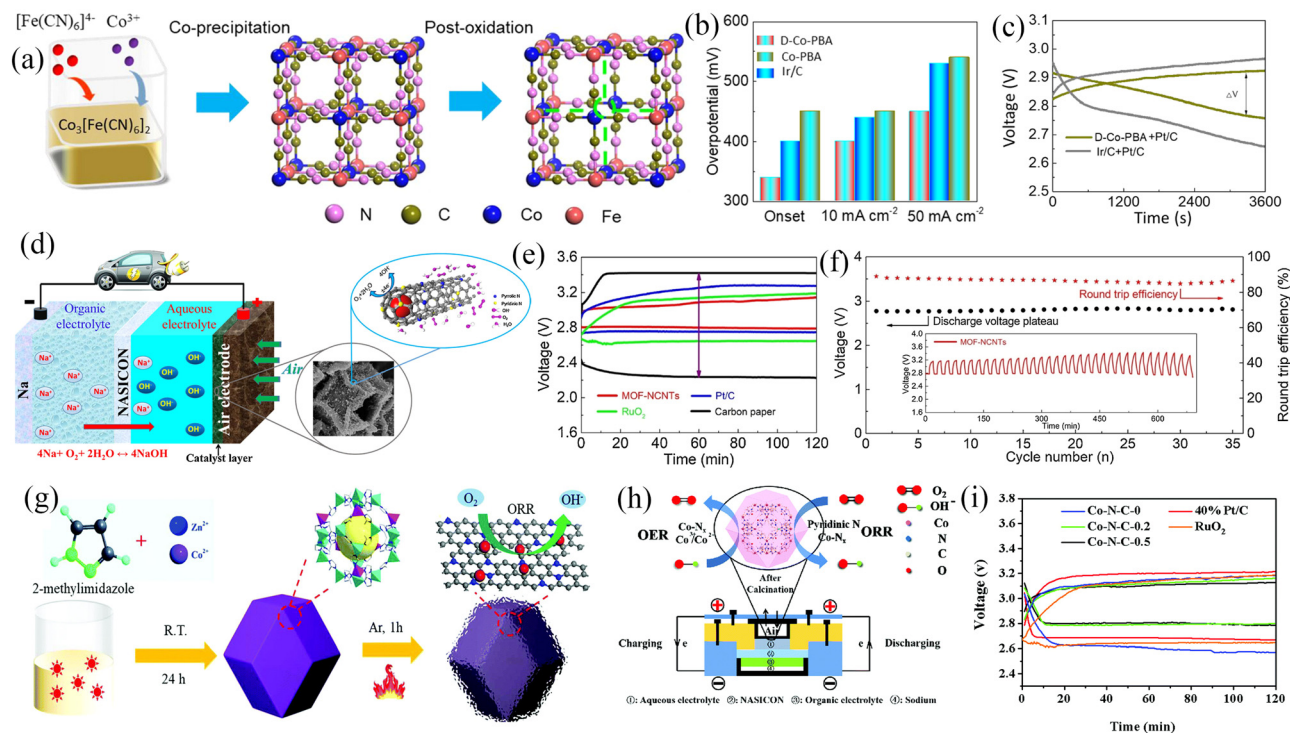


Fig. 16 (a) Schematic of synthesis route of Co-PBA and D-Co-PBA. (b) The comparison of overpotential at different states for Ir/C, Co-PBA and D-Co-PBA electrodes. (c) Charge–discharge curves of Na–O₂ batteries using different electrodes at current density of 0.01 mA cm^{-2} . (Reproduced from ref. 152 with permission from Elsevier). (d) Schematic illustration of a hybrid Na–air battery and the ORR/OER process at the surface of Co confined in MOF-NCNTs. (e) Charge–discharge curves of Na–O₂ batteries with MOF-NCNTs, Ru/O₂, Pt/C and carbon paper electrode at 0.1 mA cm^{-2} . (f) Long-stability performance of Na–air batteries with MOF-NCNTs as bifunctional catalyst at 0.1 mA cm^{-2} for 35 cycles. (Reproduced from ref. 153 with permission from Elsevier). (g) Synthesis schematic of Co–N–C–x. (h) Schematic illustration of a typical hybrid Na–air battery. (i) The discharge–charge profiles with different electrodes. (Reproduced from ref. 154 with permission from the Royal Society of Chemistry).

intermediate $\bullet\text{OH}$ and reduced the overpotential (Fig. 17i). In the OER process, Fe doping was found to be more favorable for the formation of $\bullet\text{OOH}$, and thus, Fe–NiCoP exhibited superior

OER activity (Fig. 17j). The binder-free Fe–NiCoP@C electrode was able to be stably cycled for 500 cycles at 0.01 mA cm^{-2} with the highest power density of 621 mW g^{-1} .



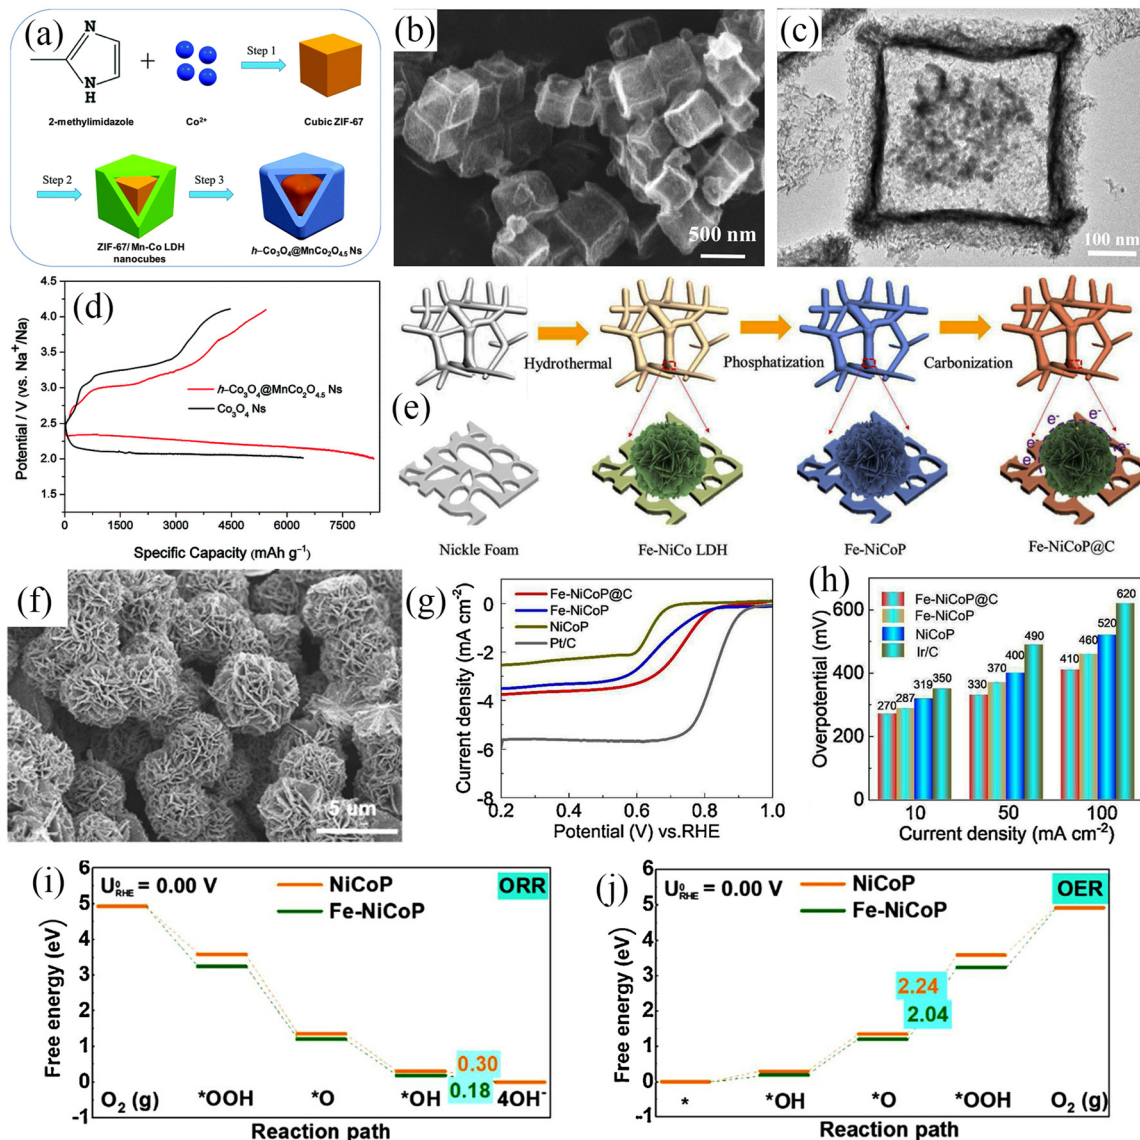


Fig. 17 (a) Scheme for the preparation of $h\text{-Co}_3\text{O}_4/\text{MnCo}_2\text{O}_{4.5}$ Ns. (b) The SEM image and (c) The TEM image of $h\text{-Co}_3\text{O}_4/\text{MnCo}_2\text{O}_{4.5}$ Ns. (d) The initial discharge/charge profiles of Na- O_2 batteries with $h\text{-Co}_3\text{O}_4/\text{MnCo}_2\text{O}_{4.5}$ Ns and Co_3O_4 Ns electrodes. (Reproduced from ref. 156 with permission from the Royal Society of Chemistry). (e) Scheme for the preparation of Fe-NiCoP@C. (f) The SEM image of Fe-NiCoP@C. (g) ORR polarization curves of NiCoP, Fe-NiCoP, Fe-NiCoP@C, and Pt/C electrode. (h) The overpotentials of NiCoP, Fe-NiCoP, Fe-NiCoP@C, and Ir/C electrode. (i and j) Calculated OER/ORR energy diagram of the NiCoP and Fe-NiCoP. (Reproduced from ref. 17 with permission from the Elsevier).

3.6. Other cathode materials

To address the shortcoming of insufficient catalytic activity for ORR and OER of Na-air cathode, many bifunctional ORR/OER electrocatalysts have been reported, such as $\text{A}_2\text{B}_2\text{O}_7$ and transition metal phosphates. Detailed information on other cathode materials and their electrochemical performance is shown in Table 6. Among them, $\text{A}_2\text{B}_2\text{O}_7$ is a type of complex oxide, where A is lanthanide or alkaline earth cation, and B is transition metal cation.^{159,166} A-site metal cation and B-site cation should have a slight difference in Pauling electronegativity (the power of an atom in a molecule to attract electrons to itself), which benefits the formation of higher-density covalent chemical bonds between B-O-B/A-site cation.¹⁶⁷ Such a high density of

chemical bonds would delocalize the electrons at the outermost orbital of the cations, creating shared electrons, therefore facilitating charge transfer within the cathodic materials over charging/discharging cycling.¹⁶² Further, the 3D network of B_2O_6 octahedra in the $\text{A}_2\text{B}_2\text{O}_7$ structure can provide atomic pathways for electron transport, resulting in higher electrical conductivity and enhanced electrocatalytic performance.¹⁵⁹ Due to the higher selectivity of metal cations, the physicochemical properties of $\text{A}_2\text{B}_2\text{O}_7$ can be regulated by controlling the types of metals, such as the substitution of the A-site or B-site. Several bifunctional catalysts are based on Ru pyrochlore oxides such as for example, $\text{Bi}_{2.4}\text{Ru}_{1.6}\text{O}_7$, $\text{Pb}_2\text{Ru}_2\text{O}_{6.5}$,¹⁶⁸ and $\text{Bi}_2\text{Ru}_2\text{O}_7$.²⁶ In 2019, Kim *et al.*²⁶ selected Bi^{3+} as the A-site



cation to synthesize $\text{Bi}_2\text{Ru}_2\text{O}_7$ nanoparticles (Fig. 18a). The *ex situ* X-ray absorption spectroscopy (XAS) results showed that Bi^{3+} and Ru^{4+} on the surface of $\text{Bi}_2\text{Ru}_2\text{O}_7$ nanoparticles became oxidized during the ORR/OER process and thus can readily be reduced through electron donation. The electrons contributed by cations are easily transported to the interior and surface of $\text{Bi}_2\text{Ru}_2\text{O}_7$ particles, which is beneficial in reducing the impedance during electrocatalysis. The Na-air cell based on the $\text{Bi}_2\text{Ru}_2\text{O}_7$ cathode exhibited a low overpotential of 211 mV and a high round-trip efficiency of 93.58% (Fig. 18b).

The electronic properties of $\text{A}_2\text{B}_2\text{O}_7$ can be tailored by substituting metal dopants at the A-site and/or B-site. This

would alter the localised electron density, affecting the interaction of the 3d electrons in the metal atoms. Jiang *et al.*¹⁵⁹ studied the role of metal dopant substitutions on the electrocatalytic performance of $\text{La}_2\text{Sn}_2\text{O}_7$ (Fig. 18c). The impact of the substitution of Sr into La (A site) on the electrochemical properties of pyrochlore oxides was studied. The FTIR and XPS results indicated that by increasing the Sr content in $\text{La}_{2-x}\text{Sr}_x\text{Sn}_2\text{O}_7$ ($x = 0, 0.2, 0.5, 1.0, 1.5, 2.0$), the length of Sn–O bond would change, which would promote the movement of oxygen in the catalyst and improve the catalytic activity. When the Sr content is increased to $x \geq 1.5$, $\text{La}_{2-x}\text{Sr}_x\text{Sn}_2\text{O}_7$ exhibits a larger specific surface area, which is also beneficial to

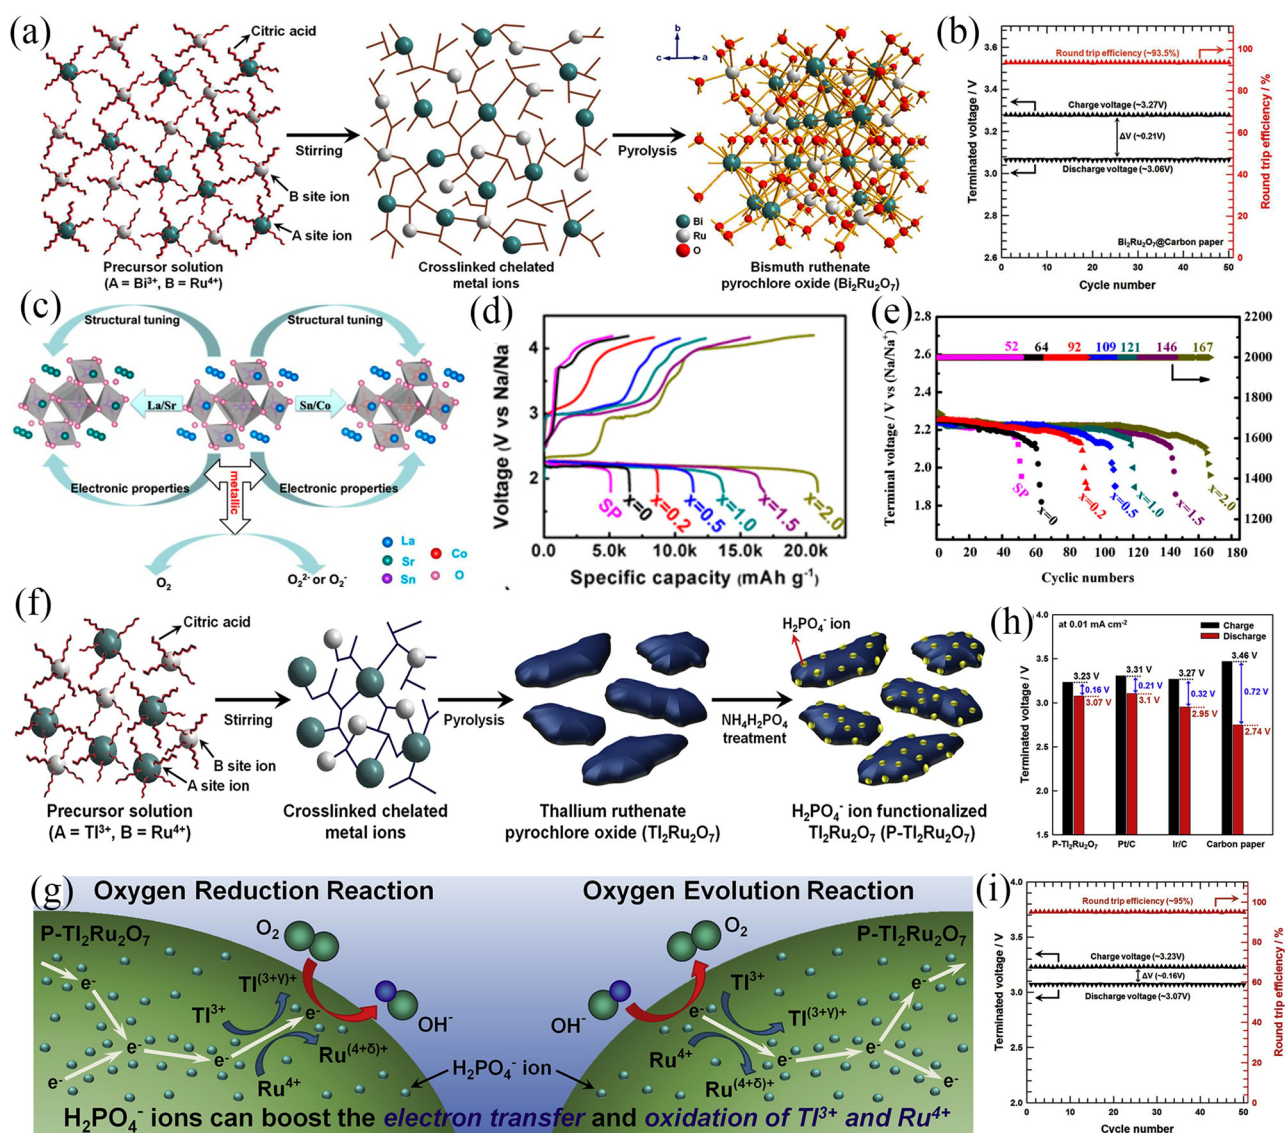


Fig. 18 (a) Schematic illustration of the preparation of $\text{Bi}_2\text{Ru}_2\text{O}_7$. (b) Cycle performance of $\text{Bi}_2\text{Ru}_2\text{O}_7$ -based cathode Na– O_2 batteries. (Reproduced from ref. 26 with permission from Elsevier). (c) Schematic illustration tuning the electronic and structural properties via adjusting the element composition of $\text{La}_2\text{Sn}_2\text{O}_7$. (d) The initial discharge-charge profiles for $\text{La}_2\text{Sn}_{2-x}\text{Co}_x\text{O}_7$ at 100 mA g^{-1} . (e) Cycle performance of $\text{La}_2\text{Sn}_{2-x}\text{Co}_x\text{O}_7$ -based cathode Na– O_2 batteries at a current density of 200 mA g^{-1} . (Reproduced from ref. 159 with permission from the American Chemical Society). (f) Schematic illustration of the preparation of P- $\text{Ti}_2\text{Ru}_2\text{O}_7$. (g) Schematic illustration of the catalytic origin of P- $\text{Ti}_2\text{Ru}_2\text{O}_7$. (h) Comparison of the overpotential of the P- $\text{Ti}_2\text{Ru}_2\text{O}_7$, Pt/C, Ir/C and carbon paper. (i) Long-term performance of P- $\text{Ti}_2\text{Ru}_2\text{O}_7$ -based cathode Na– O_2 batteries. (Reproduced from ref. 162 with permission from Elsevier).



improving the catalytic performance. When applied to the cathode of Na–O₂ battery, the first discharge-specific capacity of the La_{2–x}Sr_xSn₂O₇ catalyst regularly increased with the increase of Sr content. In addition, the change in trend of the catalytic activity of La₂Sn_{2–x}Co_xO₇ ($x = 0, 0.2, 0.5, 1.0, 1.5, 2.0$) is consistent with that of A-site substituted La₂Sn₂O₇. La₂Co₂O₇ exhibited an extremely high initial discharge specific capacity of 20 184.2 mA h g^{–1} and excellent cycling stability (167 cycles) (Fig. 18d and e). This is due to the generation of oxygen vacancies during the replacement of Sn by Co, resulting in local structural changes. The above results indicate that substituting atoms at different positions can effectively tune the electrocatalytic performance of pyrochlore oxide catalysts. In addition, the limited surface chemical reactions of pyrochlore oxides limit the development of electrocatalytic activity, and therefore surface modification of pyrochlore oxides can significantly improve their electrochemical performance. Kim *et al.*¹⁶² fabricated functionalized pyrochlore oxide (P-Tl₂Ru₂O₇) by modifying P-Tl₂Ru₂O₇ with dihydrogen phosphate ions (H₂PO₄[–]) (Fig. 18f), and applied it to the cathode of Na–air battery. After the ORR/OER process, the K-edge X-ray absorption near-edge structure (XANES) spectra of Ru in P-Tl₂Ru₂O₇ and Tl₂Ru₂O₇ shifted to higher photon energies, indicating the oxidation of metallic Ru during the electrochemical process. The L_{III}-edge XANES spectra of Tl in P-Tl₂Ru₂O₇ and Tl₂Ru₂O₇ also showed the same trend, indicating that the Tl cation showed a higher oxidation state after the ORR/OER process. The H₂PO₄[–] ions on the surface of P-Tl₂Ru₂O₇ promoted the oxidation of metal Ru and Tl, which accelerated the electron transfer to the inner layer and surface of the oxide, and further significantly reduced the electrical resistance during electrocatalysis. Meanwhile, the O 2p and Ru 4d orbitals in P-Tl₂Ru₂O₇ are highly hybridized and formed strong Ru–O covalent bonds, which improved the ORR/OER catalytic activity of P-Tl₂Ru₂O₇ (Fig. 18g). In Na–air batteries, the P-Tl₂Ru₂O₇ cathode with excellent electrochemical properties exhibited an overpotential of only 160 mV (Fig. 18h). This P-Tl₂Ru₂O₇ air cathode was stably cycled more than 50 times at a current density of 0.01 mA cm^{–2} (Fig. 18i). Furthermore, use of different A-site/B-site-cation combinations, cation substitution at different positions, and anion modification methods can help tune the electronic structure of pyrochlore oxides to improve their electrocatalytic performance.

The charging process of Na–O₂ batteries is essentially the process of oxygen evolution, which corresponds to the OER catalytic reaction. In this process, the formation of strong O=O covalent bonds is very slow, and high energy is required, which has prompted the search for bifunctional catalysts with excellent catalytic activity.¹⁶⁹ Co-based compounds are considered a class of bifunctional catalysts with excellent catalytic properties with examples being NaCoPO₄ and Na₂CoP₂O₇.¹⁷⁰ Polyanionic framework compounds composed of three-dimensional transition metals exhibit stable crystal structures and are derived from ionic/covalent bonds in three-dimensional frameworks.^{171–174} Compared to conventional oxides, cobalt-based phosphates have strong phosphate skeletons

and diverse structures, which can stabilize the intermediate species in the catalytic center of the catalytic process.¹⁶⁹ In 2020, Barpanda *et al.*¹⁶³ used a solution combustion method to synthesize porous Na₂CoPO₄F cathodes that exhibited an overpotential of only 417 mV at a current density of 10 μA cm^{–2}, which makes them very promising as a bifunctional cathode for secondary Na–O₂ batteries.

In summary, the essence of Na–air battery cathode material is a bifunctional catalyst with excellent ORR and OER catalytic activities. However, unlike conventional bifunctional catalysts, Na–air battery cathode materials need to have the ability to accommodate discharge products at the same time. An ideal cathode material for air batteries needs to satisfy the following design strategies: (i) excellent electrochemical durability/stability: electrochemical reactions with high chemical/electrochemical stability under charge/discharge and minimal irreversible reactions, improved round-trip efficiency of the battery and maintenance of long-term stability. (ii) Higher specific surface area, which provides abundant active sites: cathode materials with high surface area and mesoscale pores exhibit high NaO₂ storage capacity, enhancing the discharge capacity of the battery. A clear correlation has been shown between surface properties such as surface area and mesopore volume of air battery cathode materials and electrochemical properties such as discharge capacity. (iii) Porous structure increases mass transfer during electrochemical processes: electrodes with large pore volume facilitate electrolyte penetration and ensure that the active components (*i.e.* Na⁺ and O₂) reach the reaction sites. The adequate porosity of air electrodes not only favors the transport and accumulation of discharge products, but also determines the size of the discharge products, while contributing to the cycling stability of the battery. (iv) High conductivity: a high conductivity-air cathode helps electrons to be transferred from the poorly conductive discharge products to the cathode surface with a low overpotential.

4. Metal–air battery: *in situ* spectroelectrochemical techniques

Metal–air batteries have attracted much attention due to their outstanding specific capacity and energy density. However, the overpotential depends on the discharge products formed during the discharge process, which need to be carefully studied. Therefore, it is necessary to further study the reaction mechanism of Na–air batteries. For example (1) designing a reasonable battery material structure to improve the utilization of catalysts and to guide the distribution of discharge products without blocking the pores. (2) Exploring the factors that affect the type and shape of discharge products and adjusting the influencing factors to effectively control the discharge products and increase the cycle life of batteries. (3) The more reactive metal Na is prone to react with moisture and CO₂ in the air. However, trace amounts of water can be used to regulate the electrochemical reaction process and it is currently possible to use an absolutely dry atmosphere for electrochemical reactions.



The current research on CO₂ removal by metal–organic frameworks with porous structures provides design solutions for removing sufficient CO₂ from the air stream.^{175–177} Therefore, it is of great significance to design and study Na–air batteries that can work in an air atmosphere. (4) Advanced analytical testing methods have been used to reveal the reaction mechanisms between Na and O₂. Spectroelectrochemistry can be used to analyze changes in electrochemical cells caused by electrochemical processes. *In situ* spectroelectrochemical testing can capture *in situ* generated species by controlling the cell potential to obtain critical information for developing high-performance metal–air batteries. The spectroelectrochemical techniques include *in situ* infrared spectroscopy, *in situ* electron spin resonance, *in situ* UV/Vis spectroscopy, and *in situ* Raman spectroscopy in this section.

4.1. Infrared spectroscopy

The molecules or chemical bonds in a material are in a vibrational state at a temperature above zero Kelvin. Therefore, when the material is irradiated by infrared light, the molecules/chemical bonds produce unique absorption frequencies and can be used to identify their characteristics. Conventional infrared spectrum analysis adopts infrared transmission spectroscopy. The infrared spectrum test of the electrochemical electrode interface is often a reflection method. Common reflectance tests are diffuse reflectance infrared spectroscopy (DRIFTS), attenuated total internal reflection infrared spectroscopy (ATR-IR), and infrared reflectance absorption spectroscopy (IRAS). IRAS technology is currently widely used, but the

influence of the absorption of infrared light by the medium passing through it during the test will affect the sensitivity of the electrochemical interface. Although *ex situ* analysis is more convenient to ensure the accuracy of the results, the sample preparation process for *ex situ* testing is very cumbersome. For example, the discharge product of organic Na–O₂ battery is NaO₂, but NaO₂ is unstable in air and easily reacts with moisture, oxygen, carbon dioxide, etc. to form products that will affect the accuracy of the results. Therefore, *in situ* testing can generate more accurate information about reaction products and intermediates.

At present, many *in situ* infrared spectroscopy testing techniques have been successfully applied to metal–air batteries. In 2013, Calvo *et al.*¹⁷⁸ studied the stability of dimethyl sulfoxide (DMSO) in Li–air batteries using *in situ* infrared spectroscopy and electrochemical experiments. The results of the subtractively normalized interfacial Fourier transform infrared spectroscopy (SNIFTIS) showed no significant changes in the infrared spectra during discharge in oxygen-saturated electrolyte and during charging at 3.0–3.8 V, indicating no change in solvent composition (Fig. 19a). When charged to 4.2 V, new peaks appeared at 1295 cm⁻¹ (SO₂ asymmetric stretching vibration) and 1142 cm⁻¹ (SO₂ symmetric stretching vibration) and the peak intensity increased significantly with increasing voltage, which was attributed to the generation of dimethyl sulfone (DMSO₂) (Fig. 19b). At the same time, a positive peak appeared at 3500 cm⁻¹, which may be assigned to the O–H stretching and was caused by the consumption of trace water. The same phenomenon was also observed in the electrolyte

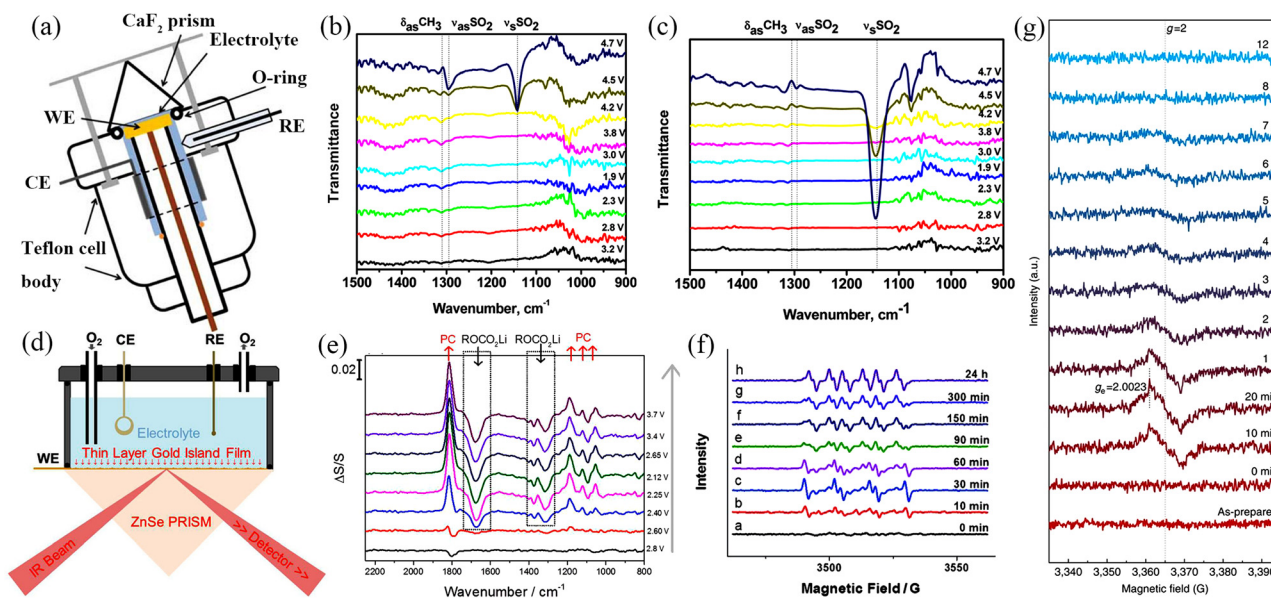


Fig. 19 (a) Schematic representation of experimental spectroelectrochemical battery. (Reproduced from ref. 180 with permission from the Electrochemical Society). (b) *In situ* IR spectra of an O₂ saturated solution of 0.1 M TBAPF₆ in DMSO. (c) *In situ* IR spectra of a deoxygenated solution of 0.1 M TBAPF₆ in DMSO. (Reproduced from ref. 178 with permission from the American Chemical Society). (d) Schematic of SEIRA spectroelectrochemical cell. (e) The SEIRA spectra result for Au thin film electrode in oxygen saturated 0.1 M LiClO₄/PC electrolyte at various electrode potentials. (Reproduced from ref 179 with permission from the American Chemical Society). (f) The ESR spectra of discharged electrolytes at the air electrode side. (Reproduced from ref. 181 with permission from Wiley). (g) The ESR results for the fresh electrolytes with soaking of the pre-discharged cathode without any aging. (Reproduced from ref. 182 with permission from Springer Nature).



without oxygen (Fig. 19c), indicating that the formation of DMSO₂ at high potential is not resulting from the presence of oxygen in the system. Hardwick and co-workers¹⁷⁹ also employed *in situ* ATR-SEIRAS to study the stability of electrolyte solvents in Li–O₂ batteries (Fig. 19d). The SEIRAS results showed that propylene carbonate (PC) in the PC–LiClO₄ system undergoes a ring-opening reaction to form carbonate (ROCO₂Li) species under the applied voltage (Fig. 19e). However, no apparent ring-opening reaction was observed in the PC–TEAClO₄ system indicating the significance of the electrolyte solute cations in the stability of PC.

4.2. Electron spin resonance

Electron spin resonance (ESR) can quantitatively and qualitatively detect unsaturated electrons in molecules and probe the structural features of their surrounding environment at the same time. ESR equipment for metal–air batteries differs from conventional testing facilities in that the components are housed in cells that can be analyzed by an ESR spectrometer, which detects free radicals generated during charge and discharge, among other products. The research on metal–air batteries has focused on discharge product composition, structure, and morphology. However, the types of intermediates during the charge–discharge process are still unclear. Zhang *et al.*¹⁸¹ detected the intermediate product of superoxide radical anion (O₂^{•−}) in the ORR process of Li–O₂ batteries. Generally, LiO₂ and O₂^{•−} are unstable and their existence time in the system is very short, so it is difficult to use ESR in this regard. Therefore, 5,5-dimethyl-pyrroline N-oxide (DMPO) was used as a free radical scavenger to capture O₂^{•−} to form a stable adduct. The long lifetime and stable ESR signal facilitate the study of intermediates in the formation of discharge products. No signal was observed at the initial stage of the discharge process, indicating that no free radicals were generated during this period. The ESR signal gradually increased as the discharge progressed, but the signal began to weaken after 30 min of discharge. When the discharge was continued for 90 min, 6 groups of new signals appeared and the appearance of new signals was attributed to the ORR process that produced O₂^{•−} (Fig. 19f). However, the phenomenon during charging is diametrically opposite to that during discharging and no obvious O₂^{•−} signal is observed. However, a new set of weak signals appeared late in the charging process, which was analysed and found to be caused by free radicals generated by the decomposition of the electrolyte under high pressure. Therefore, it shows that in the Li–O₂ battery with DMSO as the electrolyte, the discharge process is dominated by single electron transfer (O₂ → O₂^{•−} → O₂^{2−}) while the charging process involves double electron transfer (O₂^{2−} → O₂), and there is no O₂^{•−} intermediate product.

Similarly, Kang *et al.*¹⁸² used ESR to study the dissolution behaviour of NaO₂ which is the discharge product of organic Na–O₂ batteries (Fig. 19g). The ESR signal was generated after the electrode was soaked in fresh electrolyte for 10 min, indicating the production of O₂^{•−}. The signal intensity of O₂^{•−} reached the highest value after 20 min, followed by a

gradual decrease in intensity, and disappeared completely after 8 h of immersion. Combining the above experimental phenomena and literature analysis, it can be concluded that the discharge product NaO₂ will dissolve in the ether-based electrolyte to generate O₂^{•−} and Na⁺. However, due to the poor stability of O₂^{•−}, H⁺ can be extracted from the electrolyte solvent to form hydroperoxyl radicals (HO₂). In the presence of nucleophilic attack of HO₂ and oxidation reactions, the electrolyte solvent also decomposes to form carbon dioxide (CO₂), water (H₂O), and hydroxyl anions (OH[−]). At the same time, HO₂ will undergo a disproportionation reaction to form hydrogen peroxide (H₂O₂) and O₂. The above reactions occur in the same system; Na⁺, OH[−] and H₂O₂ undergo further peroxo-hydroxylation to form Na₂O₂·2H₂O. The decomposition of Na₂O₂·2H₂O requires higher energy, resulting in an increase in the overpotential of Na–O₂ batteries. Thus, ESR has shown significant advantages in studying the redox reaction mechanism of metal–air batteries.

4.3. UV/Vis spectroscopy

UV/Vis absorption spectroscopy (UV/Vis spectroscopy) of metal–air batteries has been mainly used to study intermediate products during the charge/discharge process. O₂^{•−} shows strong absorbance at 245 nm in DMSO and 306 nm in pyridine.¹⁸³ Peroxides do not have this feature and thus the intermediate product conversion process can be studied by UV/Vis spectroscopy. UV/Vis spectroscopy is normally used to study the transition of valence electrons. In metal–O₂ batteries, the main research using this technique has focussed on the n → π* and π → π* transitions of O₂^{•−}. The schematic diagram of the *in situ* UV/Vis device is shown in Fig. 20a, with indium tin oxide as cathode and Li foil as anode, and the device was assembled in a glove box.¹⁸⁴ In 2015, Ye *et al.*¹⁸⁵ conducted a detailed study of the ORR/OER process of Li–O₂ batteries using *in situ* UV/Vis spectroscopy. As shown in Fig. 20b, the electrode in the initial state did not have any absorption peak while a strong absorption peak located at 252 nm appeared when discharged to 2.0 V, which was due to the occurrence of 1π_u → 1π_g transition of O₂^{•−} in the solvent. Moreover, the peak intensity gradually increased with time, which indicated that O₂^{•−} was continuously generated during the oxygen reduction process. The absorbance decreased when the charging process was carried out, but the superoxide remained in the solution (Fig. 20c). When the cell voltage was kept at 4.0 V, the absorbance decreased with time, indicating that the oxidation reaction of superoxide was still occurring. In addition, it was proved that LiO₂ and Li₂O₂ were generated during the discharge process by *in situ* Raman spectroscopy and *in situ* surface-enhanced Raman vibrational spectroscopy. In conclusion, side reactions on Au electrodes in DMSO solution are ignored in short-term observations. On the one hand, O₂^{•−} can exist stably and form superoxide in TBAClO₄ (Li-free electrolyte)/DMSO solution; On the other hand, when using DMSO solution containing lithium-ions, the ORR process becomes complicated and oxygen is gradually reduced to form LiO₂ and Li₂O₂ on the Au electrode.



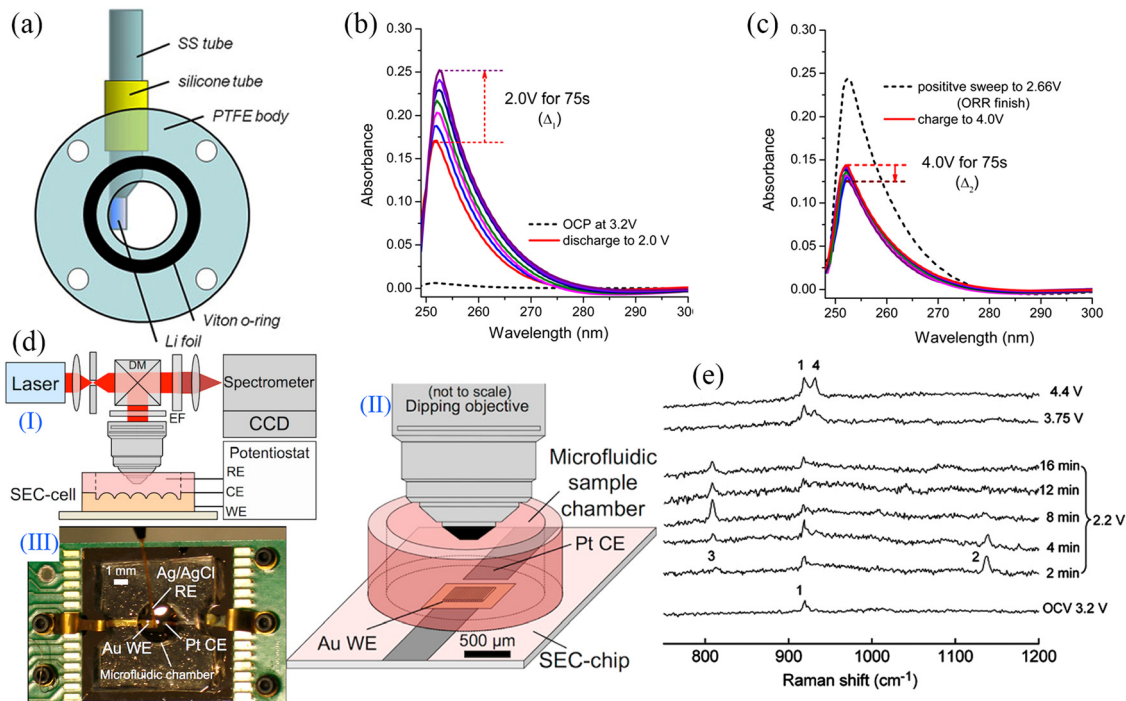


Fig. 20 (a) Schematic of *in situ* UV/Vis spectroscopy battery. (Reproduced from ref. 184 with permission from Elsevier). (b) The UV/Vis spectra of discharge electrode and (c) corresponding spectra of charge electrode in O₂-saturated TBAClO₄-DMSO. (Reproduced from ref. 185 with permission from the American Chemical Society). (d) *In situ* SERS spectroelectrochemical analysis system. (I) Schematic of the Raman analysis system. (II) Spectroelectrochemical-cell composed of a spectroelectrochemical-chip directly bonded to a small-volume microfluidic sample chamber with an optical interface to a microscope objective. (III) Spectroelectrochemical cell consisting of a Pt CE and a nanostructured Au WE patterned on the silicon spectroelectrochemical-chip and an external Ag/AgCl RE. (Reproduced from ref. 186 with permission from the American Chemical Society). (e) *In situ* SERS results during charge and discharge on Au in O₂-saturated 0.1M LiClO₄-CH₃CN. (Reproduced from ref. 187 with permission from Wiley).

4.4. Raman spectroscopy

In situ Raman spectroscopy can be used to study the detailed mechanism of the oxygen cathode interfacial reaction in Na-air batteries and the side reactions in the reaction process, but the Raman signal is often unsatisfactory. Therefore, it is necessary to use a specific method to enhance the Raman signal. First, the method of roughening the electrode surface can be used to obtain surface-enhanced Raman scattering spectroscopy (SERS) with high intensity (Fig. 20d).^{188–191} If electrochemical Raman spectroscopy is used to study the redox mechanism of metal-air batteries, the gold electrode can be used as the air cathode, which shows a strong SERS signal.¹⁹² Shell-isolated nanoparticle-enhanced Raman spectroscopy (SHINERS) can also be employed to meet experimental needs.¹⁹³ Due to the specific characteristics of metal-air batteries, it is necessary to use *in situ* Raman spectroscopy, especially for Na- and K-based systems with stronger alkali metal activity, and thus, the accuracy of the results obtained by *ex situ* techniques needs to be verified. The whole *in situ* Raman cell device is made of quartz glass and the counter electrode and the reference electrode are sealed in glass capillaries. Bruce and colleagues¹⁸⁷ used *in situ* SERS to provide strong evidence for the redox reaction mechanism of organic Li-O₂ batteries (0.1 M LiClO₄-CH₃CN). Only one peak appeared in the open-circuit voltage regime, which was attributed to the C-C

symmetric stretching in CH₃CN. Two new peaks appeared when discharged to 2.2 V, at 1137 cm⁻¹ and 808 cm⁻¹, which corresponded to the stretching of the O-O bond in LiO₂ and the O-O bond in Li₂O₂, respectively (Fig. 20e). As time increased, the amount of LiO₂ gradually decreased, while Li₂O₂ gradually increased. It has been shown that in the organic electrolyte with lithium ions, the reduction product of O₂ first combines with Li⁺ to form LiO₂, and then LiO₂ disproportionates to form a more stable Li₂O₂.

Although various electrochemical testing techniques and phase analysis techniques have been developed, it is difficult for other testing techniques other than spectroelectrochemistry to comprehensively understand electrode reactions or study complex electrode systems. Thus, *in situ* spectroelectrochemical technology provides a strong technique to support the development of high-performance metal-air batteries and has broad application prospects.

5. Summary and outlook

5.1. Summary

Rechargeable Na-air batteries have received a lot of attention due to their significant energy density and cost advantages. Firstly, the present work summarised the basic working principles of organic Na-air batteries and hybrid Na-air batteries,



which is helpful for a more in-depth study of their redox mechanisms. Although there is fierce competition between organic Na-air batteries and hybrid Na-air batteries, the essence of their discharge and charge processes is still the oxygen reduction and evolution processes, respectively. For organic Na-air batteries, the composition and morphology of the discharge products are influenced by various factors (category and surface properties of the air electrode and electrolyte composition). At the same time, the presence of organic electrolytes will result in discharge products with low conductivity and poor solubility to accumulate in the air electrode, covering the active sites, increasing the overpotential during cycling, and reducing the cycle life. In addition, organic electrolytes are expensive, flammable, and quite toxic. Thus the hybrid Na-air battery has received extensive attention due to its simple reaction process, single discharge product, high theoretical operating voltage, and long cycle life.

Next, a comprehensive summary has been provided regarding the research progress of air cathodes in Na-air batteries, which considered different material possibilities including carbon materials, transition metals and metal oxides, noble metals, perovskites and spinels, metal-organic frameworks and their derivatives, pyrochlore oxides, and others used to lesser extent. Carbon materials considered including carbon films, CNTs, CNFs, porous carbon spheres, graphene, reduced graphene oxide, and porous carbon. The results show that the content of functional groups on the surface of carbon materials can affect the morphology and types of discharge products. At the same time, carbon cathodes with abundant pores are more easily wet by the electrolyte, which will ensure full use of the abundant redox sites and enable the accommodation of more discharge products to increase cycle stability and life. Carbon cathodes are the most promising commercial air cathode materials. In addition to the above carbon-based materials with bright application prospects, transition metal-based electrocatalysts with enhanced electrochemical performance are also included, including CoB, CoP, SnS₂, CoO, Co₃O₄, Mn₂O₃, α -MnO₂, VO₂@rGO-carbon paper and Co@ECNCFs. Noble metals have received extensive attention because of their electrocatalytic reaction kinetics and improved catalytic activity since they can improve the interfacial interactions of reactants. RuO₂ nanoparticles dispersed on the surface of CNT, Pt clusters deposited on the surface of defective NiFe LDHs, Ru dispersed on the surface of CNTs, Ag nanoparticles modified rGO, and Pd nanoparticles grown on ZnO can all be used as Na-O₂ battery cathode materials. Ternary metal oxides with oxygen vacancies and crystal defects exhibit more prominent catalytic activity in comparison to binary metal oxides. Additionally, defect engineering (such as A-site/B-site substitution, oxygen vacancy and anion doping) can be employed to introduce defects in metal oxides to increase the ORR/OER activity significantly. Both pristine MOFs and MOF derivatives can exhibit excellent electrochemical performance, which arises because the MOFs assembled by metal nodes and organic ligands has a porous network structure and endows the material with a large specific surface area, which is conducive to the contact, transport and

exchange of the material, and ensures the continuous reactions as part of the oxygen reduction and oxygen evolution processes.

At the same time, it is necessary to use *in situ* spectro-electrochemical technologies (such as IR, ESR, UV/Vis Spectroscopy and Raman Spectroscopy) to monitor the intermediate products during the charging and discharging process of Na-air batteries to reveal the mechanisms related to the formation and disappearance of the discharge products, as well as the generation of side products.

6. Outlook

Na-air batteries show advantages such as low overpotential and high theoretical specific capacity and energy density, but not very obvious advantages in terms of cycling performances since side reactions on the air cathode, metal Na cathode and electrolyte limit the cycle life of Na-air batteries. Thus, there are still many challenges and possible future research directions for Na-air batteries in order to ensure their commercialization (Fig. 21).

(1) Air cathode: The electrochemical performance of Na-air batteries depend largely on the electrochemical performance of the air cathode. During the discharge process, the internal pores of the air cathode material will be gradually filled with solid discharge products, which will block O₂ diffusion and electrolyte transfer, leading to a decrease in discharge specific capacity. At the same time, the accumulation of insoluble discharge products during the deep discharge process will cause the volume expansion of the air cathode material. Due to the mutual support of discharge products and cathode material, the whole electrode structure will not change significantly. However, after the discharge products are dissolved in the subsequent charging process, the conductive electrode material connectivity of the air cathode will inevitably become reduced, which would lead to irreversible breakage of the electrode structure. Therefore, the ideal air cathode should have the following characteristics: high surface area with porous structure, high electrical conductivity, effective catalytic activity to facilitate ORR and OER processes, and sufficient mechanical strength and stability for accommodating the volume expansion during the formation and decomposition of insoluble discharge products. In this direction, current efforts should be devoted to the discovery and design of suitable anode materials, such as multidimensional nanostructured carbon materials, metal nanoparticles, transition metal oxides, perovskite/spinel oxides, and metal-organic frameworks to improve the cycle specific capacity, energy density, and cycle life of Na-air batteries. Taking perovskite/spinel oxides with excellent catalytic activity as an example, perovskite and spinel phase with excellent electrocatalytic properties, have potential for very broad application prospects in rechargeable Na-air batteries. Moreover, defect engineering can be used to enhance the catalytic activity of perovskite and spinel. Further, combining advanced characterization techniques with simulation is necessary to systematically study the effect of defect



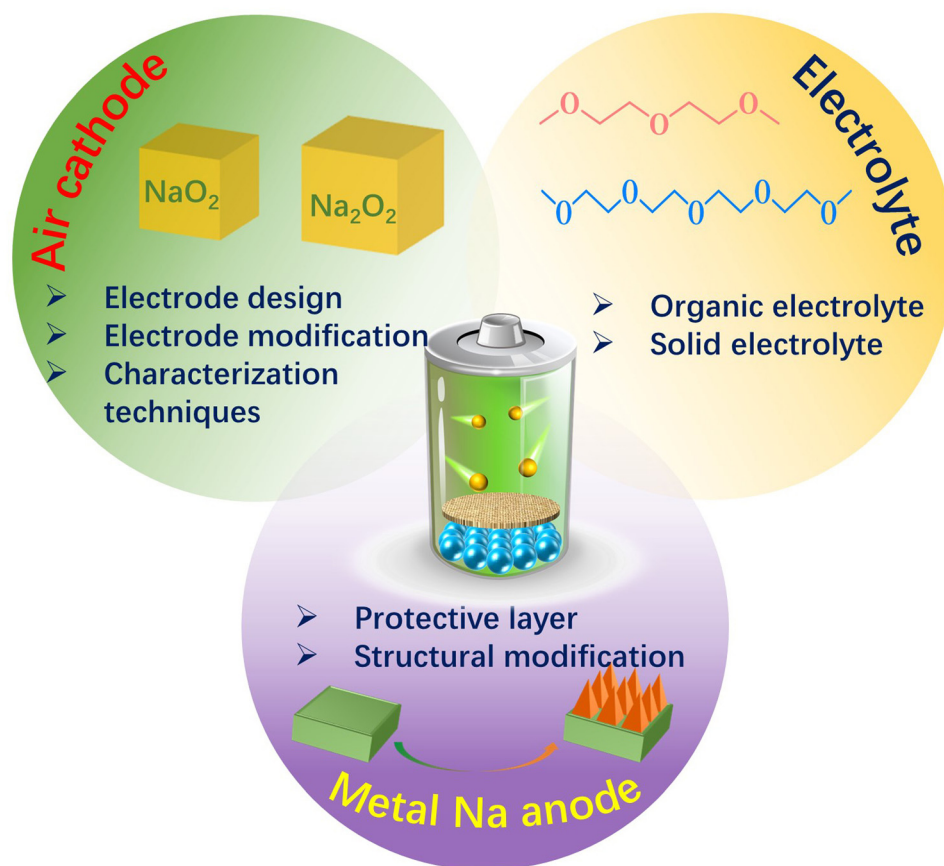


Fig. 21 The major challenges facing the development of Na-air batteries.

engineering on catalytic activity. Importantly, a large amount of research is currently devoted to studying how the physicochemical properties of air cathodes affect the composition (*i.e.* NaO_2 , Na_2O_2 or $\text{Na}_2\text{O}_2 \cdot 2\text{H}_2\text{O}$) and morphology of discharge products. Carbon cathodes with abundant pores and high specific surfaces are currently the most promising commercial cathodes. However, the mechanism of the formation and growth of different discharge products with different morphologies on electrodes is still unclear. To develop a more stable air cathode, various *in situ* and *ex situ* characterization techniques are needed to reveal the correlation between the discharge products and the properties of the air cathode. At the same time, to study more diverse and complex processes, a variety of *in situ* spectroelectrochemical techniques can be employed.

(2) Na anode: In order to improve the energy density of Na-air battery, the direct use of Na metal is beneficial to maximise the actual energy density of the battery. The metal anode loses electrons during the discharge process to form Na^+ , which diffuses through the electrolyte to the cathode side of the battery to form discharge products. During the charging process, the metal ions are deposited on the electrode surface by reduction, and their morphology is different from the initial shape. The potential gradient between the cathode and anode leads to the formation of sodium dendrites. After many charge/discharge cycles, sodium dendrites pose a serious risk to the

operation of the actual battery. Once the dendrites keep growing and completely penetrate the diaphragm, the battery may fail due to short circuit between the cathode and the anode. Adding a protective layer to the sodium metal surface is a very common strategy to reduce dendrite formation for higher cycling stability, and the protective layer can consist of a polymer solid electrolyte. The protective layer must meet the following criteria: (1) high ionic conductivity to promote uniform sodium ion transport across the electrode surface; (2) high hardness, elastic modulus, and compact structure to inhibit dendrite formation; (3) sufficient flexibility to accommodate interfacial fluctuations during sodium precipitation/deposition; and (4) capability to prevent oxygen and moisture crossover between the air electrode and the sodium anode. In addition to the above methods, the metal Na anode can be modified to reduce dendrite formation. The use of pre-sodiated hard carbon and/or hollow carbon spheres as anode material can largely reduce the formation of dendrites and improve the cycle life of the battery. However, such a measure will reduce the weight of sodium metal in the anode material and reduce the energy density of the battery.

(3) Advances *in situ/operando* characterization technologies combined with theoretical models: Elucidating the cause of poor results using conventional *ex situ* characterization techniques often requires the disassembly of metal-air batteries after



operation. Samples can often be contaminated during disassembly. In contrast, *in situ*/operational microscopy and spectroscopy combined with first-principles density functional theory (DFT) calculations can capture dynamic information during cycling, enabling real-time monitoring of the processes in the metal–air battery. These techniques also promise to illustrate what can be gained from *in situ*/operational characterization techniques and serves as a reference for research into other battery types. At present, many *in situ* infrared spectroscopy testing techniques have been successfully applied to metal–air batteries, for instance: *in situ* ATR-SEIRAS to study the stability of electrolyte solvents in Li–O₂ batteries, as well as *in situ* interfacial Fourier transform infrared spectroscopy (SNIFTIS), *in situ* IR spectra, *in situ* UV/Vis, *in situ* Raman spectroscopy and *in situ* surface-enhanced Raman vibrational spectroscopy. First-principles calculation methods based on DFT and molecular dynamics method (MD) have attracted much attention. Computational simulations can predict correlations between material properties, including phase stability, lithium diffusion behavior, interface formation energy and electrode/electrolyte interface reactions. This can reduce research time and cost. Combining *in situ*/operational characterization techniques with computational simulations can provide insight into reaction mechanisms. The obtained characterization data can also be used to verify the accuracy of computational simulations and guide the establishment of new models and the development of new methods.

(4) Electrolyte: In addition to the important air cathode and metal Na anode, the effect of the type of electrolyte, modification and addition of additives has a significant effect on the specific capacity and cycle life of Na–air batteries. It is well known that carbonate-based electrolytes are prone to decomposition forming by-products during cycling, so ether-based electrolytes with better stability are used. However, the safety and environmentally-friendly nature of organic electrolytes is yet to be resolved. It is very promising to select solid electrolytes with high ionic conductivity to assemble a solid-state secondary Na–air battery or to fabricate hybrid Na–air batteries. For hybrid Na–air batteries, using aqueous electrolytes as the cathode compartment electrolyte can reduce the overpotential and improve the cycle life. However, designing and producing NASICON separators with higher ionic conductivity may become a bottleneck for large-scale production of hybrid Na–air batteries.

List of acronyms and abbreviations

| | |
|--|--|
| H ₂ PO ₄ [−] | Dihydrogen phosphate ions |
| A ₂ B ₂ O ₇ | Pyrochlore oxide |
| AB ₂ O ₄ | Spinel oxides |
| ABO ₃ | Perovskite oxides |
| ABO _{3−δ} | Defective perovskite oxides |
| ALD | Atomic layer deposition |
| ATR-IR | Attenuated total internal reflection infrared spectroscopy |

| | |
|--|---|
| ATR-SEIRAS | Attenuated total reflectance surface enhanced infrared absorption spectroscopy |
| C@NiCo ₂ O ₄ -NAS | Sea urchin-like C@NiCo ₂ O ₄ nanoneedles |
| CNF | Carbon nanofibers |
| CNT | Carbon nanotube |
| Co-Fe@NC | Nitrogen-doped carbon-coated CoFe bimetallic nanoparticles |
| Co-N-C | Co nanoparticles-modified N-doped defect carbon framework |
| Co-PBA | Co-based Prussian blue analogs |
| DEGDME | Diethylene glycol dimethyl ether |
| DFT | First-principles calculations |
| DME | Dimethyl ether |
| DMPO | 5,5-Dimethyl-pyrroline N-oxide |
| DMSO | Dimethyl sulfoxide |
| DMSO ₂ | Dimethyl sulfone |
| DRIFTS | Diffuse reflectance infrared spectroscopy |
| ESR | Electron spin resonance |
| Fe-NiCoP | Fe-doped NiCoP |
| Fe-NiCoP@C | Carbon coating Fe-NiCoP |
| GO | Graphene oxide |
| h-Co ₃ O ₄ @MnCo ₂ O _{4.5} | Ns Hierarchical Co ₃ O ₄ @MnCo ₂ O _{4.5} nanocubes |
| IRAS | Infrared reflectance absorption spectroscopy |
| IVCT | Intervalence charge transfer |
| KO ₂ | Potassium superoxide |
| LAB | Lithium–air battery |
| LDH | Layered double hydroxide |
| LIBs | Lithium-ion batteries |
| LSV | Linear cyclic voltammetry |
| MOF-NCNFs | Nitrogen-doped carbon nanotubes |
| MOFs | Metal–organic frameworks |
| m-RuO ₂ -B-rGO | Microscale RuO ₂ -coated rGO composites |
| MWNTs | Multi-walled carbon nanotubes |
| Na ₂ CO ₃ | Sodium carbonate |
| Na ₂ O ₂ | Sodium peroxide |
| NaClO ₄ | Sodium perchlorate |
| NaO ₂ | Sodium superoxide |
| NaPF ₆ | Sodium hexafluorophosphate |
| NASICON | Na ₃ Zr ₂ Si ₂ PO ₁₂ |
| NaSO ₃ CF ₃ | Sodium trifluoromethyl sulfonate |
| NaTFSI | Sodium bis(trifluoromethanesulfonyl)imide |
| NC | Nitrogen-doped carbon |
| NCF | Nitrogen atoms into carbon nanofibers derived from polypyrrole |
| OER | Oxygen evolution reaction |
| ORR | Oxygen reduction reaction |
| PCS | Porous carbon spheres |
| Pt/Ni _x Fe-LDHs | Defect-layered double hydroxide nanosheets |
| P-Tl ₂ Ru ₂ O ₇ | Modifying P-Tl ₂ Ru ₂ O ₇ with H ₂ PO ₄ [−] |
| SABs | Sodium–air batteries |
| SEI | Solid electrolyte layer |
| SEM | Scanning electron microscopy |



Review

| | |
|--------------------|--|
| SERS | Surface-enhanced Raman scattering spectroscopy |
| SHINERS | Shell-isolated nanoparticles-enhanced Raman spectroscopy |
| SIBs | Sodium-ion batteries |
| SNIFTIS | Subtractively normalized interfacial Fourier transform infrared spectroscopy |
| TEGDME | Triethylene glycol dimethyl ether |
| TiOSO ₄ | Titanium oxysulfate |
| TMs | Transition metals |
| TMOs | Transition metal oxide |
| VGC | VO ₂ @rGO/carbon paper |
| XANES | X-ray absorption near-edge structure |
| XAS | X-ray absorption spectroscopy |
| XPS | X-ray photoelectron spectroscopy |
| XRD | X-ray diffraction |
| ZIF-67 | Cobalt 2-methylimidazole |

Author contributions

Pengcheng Mao: investigation, formal analysis, writing – original draft, writing – review & editing. Hamidreza Arandiyani: conceptualization, investigation, methodology, supervision, writing – original draft, writing – review & editing. Sajjad S. Mofarah: methodology, investigation, formal analysis, writing – review & editing. Pramod Koshy: methodology, investigation, formal analysis, writing – review & editing. Cristina Pozo-Gonzalo: methodology, investigation, resources, formal analysis, writing – review & editing. Runguo Zheng: methodology, investigation, formal analysis. Zhiyuan Wang: methodology, investigation, formal analysis. Suresh K. Bhargava: methodology, investigation, formal analysis, writing – review & editing. Yuan Wang: conceptualization, investigation, methodology, resources, supervision, writing – original draft, writing – review & editing. Hongyu Sun: conceptualization, investigation, methodology, supervision, writing – original draft, writing – review & editing. Zongping Shao: methodology, writing – review & editing. Yanguo Liu: methodology, investigation, resources, supervision, writing – review & editing.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

H. Sun and Y. Liu acknowledge funding from the National Natural Science Foundation of China (52171202, 52177208, 51971055). Yuan Wang acknowledges the financial support by the Alfred Deakin Postdoctoral Research Fellowship 2022 (PJ08390) by Deakin University. Cristina Pozo-Gonzalo acknowledges the support by the Australian Research Council Training Centre for Future Energy Storage Technologies (IC180100049), funded by the Australian Government. H. Arandiyani and S. Bhargava acknowledge financial support from the Queensland Pacific Metals (QPM).

References

- 1 R. Bird, Z. J. Baum, X. Yu and J. Ma, *ACS Energy Lett.*, 2022, **7**, 736–740.
- 2 J. Li and X.-G. Sun, *Chem*, 2021, **7**, 1705–1707.
- 3 M. Li, J. Lu, Z. Chen and K. Amine, *Adv. Mater.*, 2018, **30**, 1800561.
- 4 T. Hosaka, K. Kubota, A. S. Hameed and S. Komaba, *Chem. Rev.*, 2020, **120**, 6358–6466.
- 5 H. Zhao, W.-Y. A. Lam, L. Wang, H. Xu, W. A. Daoud and X. He, *Energy Environ. Sci.*, 2022, **15**, 2329–2355.
- 6 J. Mao, C. Ye, S. Zhang, F. Xie, R. Zeng, K. Davey, Z. Guo and S. Qiao, *Energy Environ. Sci.*, 2022, **15**, 2732–2752.
- 7 J. C. Stallard, L. Wheatcroft, S. G. Booth, R. Boston, S. A. Corr, M. F. L. De Volder, B. J. Inkson and N. A. Fleck, *Joule*, 2022, **6**, 984–1007.
- 8 Y. Liu, H. Zhang, N. Jiang, W. Zhang, H. Arandiyani, Z. Wang, S. Luo, F. Fang and H. Sun, *J. Alloys Compd.*, 2020, **834**, 155030.
- 9 P. Mao, H. Fan, G. Zhou, H. Arandiyani, C. Liu, G. Lan, Y. Wang, R. Zheng, Z. Wang, S. K. Bhargava, H. Sun and Y. Liu, *J. Colloid Interface Sci.*, 2023, **634**, 63–73.
- 10 H. Fan, C. Liu, G. Lan, P. Mao, R. Zheng, Z. Wang, Y. Liu and H. Sun, *Electrochim. Acta*, 2023, **439**, 141614.
- 11 Z. Zheng, J. Jiang, H. Guo, C. Li, K. Konstantinov, Q. Gu and J. Wang, *Nano Energy*, 2021, **81**, 105529.
- 12 L. Zhang, Q. Zhuang, R. Zheng, Z. Wang, H. Sun, H. Arandiyani, Y. Wang, Y. Liu and Z. Shao, *Energy Storage Mater.*, 2022, **49**, 299–338.
- 13 H.-F. Wang and Q. Xu, *Matter*, 2019, **1**, 565–595.
- 14 X. Lin, J. Wang, X. Gao, S. Wang, Q. Sun, J. Luo, C. Zhao, Y. Zhao, X. Yang, C. Wang, R. Li and X. Sun, *Chem. Mater.*, 2020, **32**, 3018–3027.
- 15 J. Wang, R. Gao, L. Zheng, Z. Chen, Z. Wu, L. Sun, Z. Hu and X. Liu, *ACS Catal.*, 2018, **8**, 8953–8960.
- 16 C. Murugesan, S. P. Panjalingam, S. Lochab, R. K. Rai, X. Zhao, D. Singh, R. Ahuja and P. Barpanda, *Nano Energy*, 2021, **89**, 106485.
- 17 Y. Kang, S. Wang, S. Zhu, H. Gao, K. S. Hui, C.-Z. Yuan, H. Yin, F. Bin, X.-L. Wu, W. Mai, L. Zhu, M. Hu, F. Liang, F. Chen and K. N. Hui, *Appl. Catal., B*, 2021, **285**, 119786.
- 18 X. Jin, Y. Li, S. Zhang, J. Zhang, Z. Shen, C. Zhong, Z. Cai, C. Hu and H. Zhang, *Chin. Chem. Lett.*, 2022, **33**, 491–496.
- 19 K. M. Abraham and Z. Jiang, *J. Electrochem. Soc.*, 1996, **143**, 1–5.
- 20 L.-N. Song, W. Zhang, Y. Wang, X. Ge, L.-C. Zou, H.-F. Wang, X.-X. Wang, Q.-C. Liu, F. Li and J.-J. Xu, *Nat. Commun.*, 2020, **11**, 2191.
- 21 X. Shen, S. Zhang, Y. Wu and Y. Chen, *ChemSusChem*, 2019, **12**, 104–114.
- 22 Z. Zheng, C. Wu, Q. Gu, K. Konstantinov and J. Wang, *Energy Environ. Mater.*, 2021, **4**, 158–177.
- 23 P. Shen, B. Zhang, Y. Wang, X. Liu, C. Yu, T. Xu, S. S. Mofarah, Y. Yu, Y. Liu, H. Sun and H. Arandiyani, *J. Nanostruct. Chem.*, 2021, **11**, 33–68.



- 24 H. Fan, P. Mao, H. Sun, Y. Wang, S. S. Mofarah, P. Koshy, H. Arandiyani, Z. Wang, Y. Liu and Z. Shao, *Mater. Horiz.*, 2022, **9**, 524–546.
- 25 H. Yadegari and X. Sun, *Trends Chem.*, 2020, **2**, 241–253.
- 26 M. Kim, H. Ju and J. Kim, *Chem. Eng. J.*, 2019, **358**, 11–19.
- 27 J.-L. Ma, F.-L. Meng, D. Xu and X.-B. Zhang, *Energy Storage Mater.*, 2017, **6**, 1–8.
- 28 Q. Sun, Y. Yang and Z.-W. Fu, *Electrochem. Commun.*, 2012, **16**, 22–25.
- 29 J. Chen, B. Zhang, L. Qian, H. Wan, T. Yu, Z. Wei, Z. Wang, S. Luo, H. Arandiyani, Y. Liu and H. Sun, *J. Alloys Compd.*, 2021, **850**, 156858.
- 30 E. Peled, D. Golodnitsky, H. Mazor, M. Goor and S. Avshalomov, *J. Power Sources*, 2011, **196**, 6835–6840.
- 31 J.-l Ma, W.-c Zhang, X.-d Wang, M. Tang, Z.-y Huang, J. Li, H. Zhang, X.-h Yang, Z.-p Guo and Y. Wang, *Nano Energy*, 2021, **84**, 105927.
- 32 P. Hartmann, C. L. Bender, M. Vračar, A. K. Dürr, A. Garsuch, J. Janek and P. Adelhelm, *Nat. Mater.*, 2013, **12**, 228–232.
- 33 B. Sun, C. Pompe, S. Dongmo, J. Zhang, K. Kretschmer, D. Schröder, J. Janek and G. Wang, *Adv. Mater. Technol.*, 2018, **3**, 1800110.
- 34 C. L. Bender, D. Schröder, R. Pinedo, P. Adelhelm and J. Janek, *Angew. Chem., Int. Ed.*, 2016, **55**, 4640–4649.
- 35 S. M. B. Khajehbashi, L. Xu, G. Zhang, S. Tan, Y. Zhao, L.-S. Wang, J. Li, W. Luo, D.-L. Peng and L. Mai, *Nano Lett.*, 2018, **18**, 3934–3942.
- 36 W.-J. Kwak, L. Luo, H.-G. Jung, C. Wang and Y.-K. Sun, *ACS Energy Lett.*, 2018, **3**, 393–399.
- 37 T. A. Ha, C. Pozo-Gonzalo, K. Nairn, D. R. MacFarlane, M. Forsyth and P. C. Howlett, *Sci. Rep.*, 2020, **10**, 7123.
- 38 Y. Zhang, N. Ortiz-Vitoriano, B. Acebedo, L. O'Dell, D. R. MacFarlane, T. Rojo, M. Forsyth, P. C. Howlett and C. Pozo-Gonzalo, *J. Phys. Chem. C*, 2018, **122**, 15276–15286.
- 39 T. Wang, Y. Han, P. Xu, X. Feng, W. Ji and H. Arandiyani, *Chem. Eng. J.*, 2022, 138245, DOI: [10.1016/j.cej.2022.138245](https://doi.org/10.1016/j.cej.2022.138245).
- 40 J. Kim, H.-D. Lim, H. Gwon and K. Kang, *Phys. Chem. Chem. Phys.*, 2013, **15**, 3623–3629.
- 41 L. Lutz, D. Alves Dalla Corte, M. Tang, E. Salager, M. Deschamps, A. Grimaud, L. Johnson, P. G. Bruce and J.-M. Tarascon, *Chem. Mater.*, 2017, **29**, 6066–6075.
- 42 M. Balaish, A. Kraysberg and Y. Ein-Eli, *Phys. Chem. Chem. Phys.*, 2014, **16**, 2801–2822.
- 43 Z. Khan, M. Vagin and X. Crispin, *Adv. Sci.*, 2020, **7**, 1902866.
- 44 C. Xu, K. Zhang, D. Zhang, S. Chang, F. Liang, P. Yan, Y. Yao, T. Qu, J. Zhan, W. Ma, B. Yang, Y. Dai and X. Sun, *Nano Energy*, 2020, **68**, 104318.
- 45 X. Xu, K. S. Hui, D. A. Dinh, K. N. Hui and H. Wang, *Mater. Horiz.*, 2019, **6**, 1306–1335.
- 46 Y. Zhou, F. Chen, H. Arandiyani, P. Guan, Y. Liu, Y. Wang, C. Zhao, D. Wang and D. Chu, *J. Energy Chem.*, 2021, **57**, 516–542.
- 47 M. Enterría, M. Reynaud, J. I. Paredes, L. Medinilla, R. Younesi and N. Ortiz-Vitoriano, *J. Energy Chem.*, 2022, **68**, 709–720.
- 48 X. Li, Z. Zhang, M. Shen, Z. Wang, R. Zheng, H. Sun, Y. Liu, D. Wang and C. Liu, *J. Colloid Interface Sci.*, 2022, **628**, 242–251.
- 49 C. Duan, X. Li, D. Wang, Z. Wang, H. Sun, R. Zheng and Y. Liu, *Sustainable Energy Fuels*, 2022, **6**, 1479–1488.
- 50 Y. Li, H. Yadegari, X. Li, M. N. Banis, R. Li and X. Sun, *Chem. Commun.*, 2013, **49**, 11731–11733.
- 51 W. Liu, Q. Sun, Y. Yang, J.-Y. Xie and Z.-W. Fu, *Chem. Commun.*, 2013, **49**, 1951–1953.
- 52 Z. Jian, Y. Chen, F. Li, T. Zhang, C. Liu and H. Zhou, *J. Power Sources*, 2014, **251**, 466–469.
- 53 W.-J. Kwak, Z. Chen, C. S. Yoon, J.-K. Lee, K. Amine and Y.-K. Sun, *Nano Energy*, 2015, **12**, 123–130.
- 54 Q. Sun, H. Yadegari, M. N. Banis, J. Liu, B. Xiao, B. Wang, S. Lawes, X. Li, R. Li and X. Sun, *Nano Energy*, 2015, **12**, 698–708.
- 55 C. L. Bender, P. Hartmann, M. Vračar, P. Adelhelm and J. Janek, *Adv. Energy Mater.*, 2014, **4**, 1301863.
- 56 S. Kang, Y. Mo, S. P. Ong and G. Ceder, *Nano Lett.*, 2014, **14**, 1016–1020.
- 57 B. Lee, J. Kim, G. Yoon, H.-D. Lim, I.-S. Choi and K. Kang, *Chem. Mater.*, 2015, **27**, 8406–8413.
- 58 P. Hartmann, M. Heinemann, C. L. Bender, K. Graf, R.-P. Baumann, P. Adelhelm, C. Heiliger and J. Janek, *J. Phys. Chem. C*, 2015, **119**, 22778–22786.
- 59 J. E. Nichols and B. D. McCloskey, *J. Phys. Chem. C*, 2017, **121**, 85–96.
- 60 C. Xia, R. Black, R. Fernandes, B. Adams and L. F. Nazar, *Nat. Chem.*, 2015, **7**, 496–501.
- 61 M. S. Jung, S. Ha, D. Koo and K. T. Lee, *J. Phys. Chem. C*, 2020, **124**, 7644–7651.
- 62 N. Ortiz-Vitoriano, T. P. Batcho, D. G. Kwabi, B. Han, N. Pour, K. P. C. Yao, C. V. Thompson and Y. Shao-Horn, *J. Phys. Chem. Lett.*, 2015, **6**, 2636–2643.
- 63 Y. Hu, X. Han, Q. Zhao, J. Du, F. Cheng and J. Chen, *J. Mater. Chem. A*, 2015, **3**, 3320–3324.
- 64 L. Lutz, D. A. D. Corte, Y. Chen, D. Batuk, L. R. Johnson, A. Abakumov, L. Yate, E. Azaceta, P. G. Bruce, J.-M. Tarascon and A. Grimaud, *Adv. Energy Mater.*, 2018, **8**, 1701581.
- 65 F. Wu, Y. Xing, J. Lai, X. Zhang, Y. Ye, J. Qian, L. Li and R. Chen, *Adv. Funct. Mater.*, 2017, **27**, 1700632.
- 66 M. Fathi Tovini, M. Hong, J. Park, M. Demirtaş, D. Toffoli, H. Ustunel, H. R. Byon and E. Yilmaz, *J. Phys. Chem. C*, 2018, **122**, 19678–19686.
- 67 F. Liang and K. Hayashi, *J. Electrochem. Soc.*, 2015, **162**, A1215–A1219.
- 68 S. Park, Z. Khan, T. J. Shin, Y. Kim and H. Ko, *J. Mater. Chem. A*, 2019, **7**, 1564–1573.
- 69 J. Mei, T. Liao, J. Liang, Y. Qiao, S. X. Dou and Z. Sun, *Adv. Energy Mater.*, 2020, **10**, 1901997.
- 70 D. Cao, Y. Bai, J. Zhang, G. Tan and C. Wu, *Nano Energy*, 2021, **89**, 106464.
- 71 H. Yadegari, M. N. Banis, B. Xiao, Q. Sun, X. Li, A. Lushington, B. Wang, R. Li, T.-K. Sham, X. Cui and X. Sun, *Chem. Mater.*, 2015, **27**, 3040–3047.



- 72 N. Zhao, C. Li and X. Guo, *Phys. Chem. Chem. Phys.*, 2014, **16**, 15646–15652.
- 73 H. Yadegari, C. J. Franko, M. N. Banis, Q. Sun, R. Li, G. R. Goward and X. Sun, *J. Phys. Chem. Lett.*, 2017, **8**, 4794–4800.
- 74 N. Ortiz-Vitoriano, I. Monterrubio, L. Garcia-Quintana, J. M. López del Amo, F. Chen, T. Rojo, P. C. Howlett, M. Forsyth and C. Pozo-Gonzalo, *ACS Energy Lett.*, 2020, **5**, 903–909.
- 75 C. Shu, Y. Lin, B. Zhang, S. B. Abd Hamid and D. Su, *J. Mater. Chem. A*, 2016, **4**, 6610–6619.
- 76 B. Sun, K. Kretschmer, X. Xie, P. Munroe, Z. Peng and G. Wang, *Adv. Mater.*, 2017, **29**, 1606816.
- 77 M. Enterría, C. Botas, J. L. Gómez-Urbano, B. Acebedo, J. M. López del Amo, D. Carriazo, T. Rojo and N. Ortiz-Vitoriano, *J. Mater. Chem. A*, 2018, **6**, 20778–20787.
- 78 S. Zhang, Z. Wen, J. Jin, T. Zhang, J. Yang and C. Chen, *J. Mater. Chem. A*, 2016, **4**, 7238–7244.
- 79 J.-l Ma and X.-b Zhang, *J. Mater. Chem. A*, 2016, **4**, 10008–10013.
- 80 L. Ma, J. Li, H. Arandiyán, W. Shi, C. Liu and L. Fu, *Catal. Today*, 2012, **184**, 145–152.
- 81 H. Li, T. A. Ha, N. Ortiz-Vitoriano, X. Wang, J. Fang, P. C. Howlett and C. Pozo-Gonzalo, *J. Mater. Chem. A*, 2022, **10**, 11742–11754.
- 82 J.-l Ma, N. Li, Q. Zhang, X.-b Zhang, J. Wang, K. Li, X.-f Hao and J.-m Yan, *Energy Environ. Sci.*, 2018, **11**, 2833–2838.
- 83 Z. Khan, N. Parveen, S. A. Ansari, S. T. Senthilkumar, S. Park, Y. Kim, M. H. Cho and H. Ko, *Electrochim. Acta*, 2017, **257**, 328–334.
- 84 Q. Sun, J. Liu, X. Li, B. Wang, H. Yadegari, A. Lushington, M. N. Banis, Y. Zhao, W. Xiao, N. Chen, J. Wang, T.-K. Sham and X. Sun, *Adv. Funct. Mater.*, 2017, **27**, 1606662.
- 85 N. Li, D. Xu, D. Bao, J. Ma and X. Zhang, *Chin. J. Catal.*, 2016, **37**, 1172–1179.
- 86 N. Parveen, Z. Khan, S. A. Ansari, S. Park, S. T. Senthilkumar, Y. Kim, H. Ko and M. H. Cho, *Chem. Eng. J.*, 2019, **360**, 415–422.
- 87 S. Rosenberg and A. Hintennach, *J. Power Sources*, 2015, **274**, 1043–1048.
- 88 Z. Khan, B. Senthilkumar, S. O. Park, S. Park, J. Yang, J. H. Lee, H.-K. Song, Y. Kim, S. K. Kwak and H. Ko, *J. Mater. Chem. A*, 2017, **5**, 2037–2044.
- 89 Y. J. Sa, K. Kwon, J. Y. Cheon, F. Kleitz and S. H. Joo, *J. Mater. Chem. A*, 2013, **1**, 9992–10001.
- 90 Y. Liang, Y. Li, H. Wang, J. Zhou, J. Wang, T. Regier and H. Dai, *Nat. Mater.*, 2011, **10**, 780–786.
- 91 X.-d Wang, X. Zhang, M. Tang, Q.-y Shen and J.-l Ma, *J. Alloys Compd.*, 2021, **882**, 160702.
- 92 Z. Khan, S. Park, S. M. Hwang, J. Yang, Y. Lee, H.-K. Song, Y. Kim and H. Ko, *NPG Asia Mater.*, 2016, **8**, e294–e294.
- 93 W.-M. Liu, W.-W. Yin, F. Ding, L. Sang and Z.-W. Fu, *Electrochem. Commun.*, 2014, **45**, 87–90.
- 94 Y. Kang, D. Zou, J. Zhang, F. Liang, K. Hayashi, H. Wang, D. Xue, K. Chen, K. R. Adair and X. Sun, *Electrochim. Acta*, 2017, **244**, 222–229.
- 95 Y. Liu, X. Chi, Q. Han, Y. Du, J. Yang and Y. Liu, *J. Alloys Compd.*, 2019, **772**, 693–702.
- 96 A. Hu, C. Shu, C. Xu, R. Liang, J. Li, R. Zheng, M. Li and J. Long, *J. Mater. Chem. A*, 2019, **7**, 21605–21633.
- 97 C. Shu, C. Wu, J. Long, H. Guo, S.-X. Dou and J. Wang, *Nano Energy*, 2019, **57**, 166–175.
- 98 X. Yu, J. Guo, B. Li, J. Xu, P. Gao, K. S. Hui, K. N. Hui and H. Shao, *ACS Appl. Mater. Interfaces*, 2021, **13**, 26891–26903.
- 99 J.-H. Kang, W.-J. Kwak, D. Aurbach and Y.-K. Sun, *J. Mater. Chem. A*, 2017, **5**, 20678–20686.
- 100 S. Kumar, B. Kishore and N. Munichandraiah, *RSC Adv.*, 2016, **6**, 63477–63479.
- 101 L. Ma, D. Zhang, Y. Lei, Y. Yuan, T. Wu, J. Lu and K. Amine, *ACS Energy Lett.*, 2018, **3**, 276–277.
- 102 S. Zhang, Z. Wen, K. Rui, C. Shen, Y. Lu and J. Yang, *J. Mater. Chem. A*, 2015, **3**, 2568–2571.
- 103 M. F. Tovini, B. Patil, C. Koz, T. Uyar and E. Yilmaz, *Nanotechnology*, 2018, **29**, 475401.
- 104 X. Yu, Y. Kang, S. Wang, K. S. Hui, K. N. Hui, H. Zhao, J. Li, B. Li, J. Xu, L. Chen and H. Shao, *J. Mater. Chem. A*, 2020, **8**, 16355–16365.
- 105 S. Angel, J. Neises, M. Dreyer, K. Friedel Ortega, M. Behrens, Y. Wang, H. Arandiyán, C. Schulz and H. Wiggers, *AIChE J.*, 2020, **66**, e16748.
- 106 Y. Wang, X. Shen, H. Arandiyán, Y. Yin, F. Sun, X. Chen, M. Garbrecht, L. Han, G. G. Andersson and C. Zhao, *J. Power Sources*, 2020, **478**, 228748.
- 107 S. Angel, J. Neises, M. Dreyer, K. Friedel Ortega, M. Behrens, Y. Wang, H. Arandiyán, C. Schulz and H. Wiggers, *AIChE J.*, 2020, **66**, e16748.
- 108 Y. Wang, H. Arandiyán, J. Scott, H. Dai and R. Amal, *Adv. Sustainable Syst.*, 2018, **2**, 1700119.
- 109 N. Habibi, Y. Wang, H. Arandiyán and M. Rezaei, *Chem-CatChem*, 2016, **8**, 3600–3610.
- 110 H. Arandiyán, Y. Wang, H. Sun, M. Rezaei and H. Dai, *Chem. Commun.*, 2018, **54**, 6484–6502.
- 111 S. C. Tidrow, *Ferroelectrics*, 2014, **470**, 13–27.
- 112 Q. Ji, L. Bi, J. Zhang, H. Cao and X. S. Zhao, *Energy Environ. Sci.*, 2020, **13**, 1408–1428.
- 113 J. Li, K. He, Q. Meng, X. Li, Y. Zhu, S. Hwang, K. Sun, H. Gan, Y. Zhu, Y. Mo, E. A. Stach and D. Su, *ACS Nano*, 2016, **10**, 9577–9585.
- 114 P. Liu, Y. Liao, J. Li, L. Chen, M. Fu, P. Wu, R. Zhu, X. Liang, T. Wu and D. Ye, *J. Colloid Interface Sci.*, 2021, **594**, 713–726.
- 115 Y. Wang, H. Arandiyán, J. Scott, H. Dai and R. Amal, *Adv. Sustainable Syst.*, 2018, 1700119, DOI: [10.1002/adsu.201700119](https://doi.org/10.1002/adsu.201700119).
- 116 Y. Wang, H. Arandiyán, X. Chen, T. Zhao, X. Bo, Z. Su and C. Zhao, *J. Phys. Chem. C*, 2020, **124**, 9971–9978.
- 117 M. T. Le, P. A. Nguyen, T. T. H. Tran, T. H. N. Chu, Y. Wang and H. Arandiyán, *Top. Catal.*, 2022, **66**, 117–125.
- 118 H. Arandiyán, S. S. Mofarah, C. C. Sorrell, E. Doustkhah, B. Sajjadi, D. Hao, Y. Wang, H. Sun, B.-J. Ni, M. Rezaei, Z. Shao and T. Maschmeyer, *Chem. Soc. Rev.*, 2021, **50**, 10116–10211.



- 119 H. Arandiyani, S. S. Mofarah, Y. Wang, C. Cazorla, D. Jampaiah, M. Garbrecht, K. Wilson, A. F. Lee, C. Zhao and T. Maschmeyer, *Chem. – Eur. J.*, 2021, **27**, 14418–14426.
- 120 Y. S. Kim, G.-H. Lee, M.-C. Sung and D.-W. Kim, *Chem. Eng. J.*, 2021, **406**, 126896.
- 121 M. Xu, X. Hou, X. Yu, Z.-F. Ma, J. Yang and X. Yuan, *J. Electrochem. Soc.*, 2019, **166**, F406–F413.
- 122 J. G. Kim, Y. Noh, Y. Kim, S. Lee and W. B. Kim, *Nanoscale*, 2017, **9**, 5119–5128.
- 123 Q. Zhao, Z. Yan, C. Chen and J. Chen, *Chem. Rev.*, 2017, **117**, 10121–10211.
- 124 J. Béjar, L. Álvarez-Contreras, J. Ledesma-García, N. Arjona and L. G. Arriaga, *J. Mater. Chem. A*, 2020, **8**, 8554–8565.
- 125 X. Han, H. Sheng, C. Yu, T. W. Walker, G. W. Huber, J. Qiu and S. Jin, *ACS Catal.*, 2020, **10**, 6741–6752.
- 126 Q. Sun, X. Lin, H. Yadegari, W. Xiao, Y. Zhao, K. R. Adair, R. Li and X. Sun, *J. Mater. Chem. A*, 2018, **6**, 1473–1484.
- 127 H. Wang, X. Chen, D. Huang, M. Zhou, D. Ding and H. Luo, *ChemCatChem*, 2020, **12**, 2768–2775.
- 128 W. Xu, N. Apodaca, H. Wang, L. Yan, G. Chen, M. Zhou, D. Ding, P. Choudhury and H. Luo, *ACS Catal.*, 2019, **9**, 5074–5083.
- 129 X. Liu, L. Zhang, Y. Zheng, Z. Guo, Y. Zhu, H. Chen, F. Li, P. Liu, B. Yu, X. Wang, J. Liu, Y. Chen and M. Liu, *Adv. Sci.*, 2019, **6**, 1801898.
- 130 S. She, J. Yu, W. Tang, Y. Zhu, Y. Chen, J. Sunarso, W. Zhou and Z. Shao, *ACS Appl. Mater. Interfaces*, 2018, **10**, 11715–11721.
- 131 A. Ashok, A. Kumar, J. Ponraj, S. A. Mansour and F. Tarlochan, *Catal. Today*, 2021, **375**, 484–493.
- 132 Y. Zhang, F. Feng, C. Zhang, Q. Zheng, C. Wang, H. Hu, M. Wu and Y. Guo, *Energy Fuels*, 2020, **34**, 10170–10177.
- 133 J. Suntivich, H. A. Gasteiger, N. Yabuuchi, H. Nakanishi, J. B. Goodenough and Y. Shao-Horn, *Nat. Chem.*, 2011, **3**, 546–550.
- 134 Y. Lv, Z. Li, Y. Yu, J. Yin, K. Song, B. Yang, L. Yuan and X. Hu, *J. Alloys Compd.*, 2019, **801**, 19–26.
- 135 Y. Zhu, W. Zhou, J. Yu, Y. Chen, M. Liu and Z. Shao, *Chem. Mater.*, 2016, **28**, 1691–1697.
- 136 H. Lee, O. Gwon, C. Lim, J. Kim, O. Galindez and G. Kim, *ChemElectroChem*, 2019, **6**, 3154–3159.
- 137 J.-I. Jung, H. Y. Jeong, J.-S. Lee, M. G. Kim and J. Cho, *Angew. Chem., Int. Ed.*, 2014, **53**, 4582–4586.
- 138 K. Lopez, G. Park, H. J. Sun, J. C. An, S. Eom and J. Shim, *J. Appl. Electrochem.*, 2015, **45**, 313–323.
- 139 K. Li, M. Yin, Z. Wang, X. Chen, T. Zhu, J. Wang, N. Dewangan, Y. Yu, Q. Zhong and S. Kawi, *ChemistrySelect*, 2018, **3**, 12424–12429.
- 140 J. Ran, T. Wang, J. Zhang, Y. Liu, C. Xu, S. Xi and D. Gao, *Chem. Mater.*, 2020, **32**, 3439–3446.
- 141 Z. Li, L. Lv, J. Wang, X. Ao, Y. Ruan, D. Zha, G. Hong, Q. Wu, Y. Lan, C. Wang, J. Jiang and M. Liu, *Nano Energy*, 2018, **47**, 199–209.
- 142 Q. A. Islam, R. Majee and S. Bhattacharyya, *J. Mater. Chem. A*, 2019, **7**, 19453–19464.
- 143 L. Gui, Z. Wang, K. Zhang, B. He, Y. Liu, W. Zhou, J. Xu, Q. Wang and L. Zhao, *Appl. Catal., B*, 2020, **266**, 118656.
- 144 J. Cheng, Z. Wang, L. Zou, M. Zhang, G. Zhang, Y. Dong, Y. Jiang, Y. Huang, N. Nakashima and B. Chi, *J. Alloys Compd.*, 2020, **831**, 154728.
- 145 J. Zhou and B. Wang, *Chem. Soc. Rev.*, 2017, **46**, 6927–6945.
- 146 P. Mao, G. Lan, C. Liu, Z. Wang, Y. Liu, H. Sun and W. Huang, *SM&T*, 2021, **30**, e00354.
- 147 P. Mao, H. Fan, C. Liu, G. Lan, W. Huang, Z. Li, H. Mahmoud, R. Zheng, Z. Wang, H. Sun and Y. Liu, *Sustainable Energy Fuels*, 2022, **6**, 4075–4084.
- 148 B. Zhu, Z. Liang, D. Xia and R. Zou, *Energy Storage Mater.*, 2019, **23**, 757–771.
- 149 Y. Wang, B. Liu, X. Shen, H. Arandiyani, T. Zhao, Y. Li, M. Garbrecht, Z. Su, L. Han, A. Tricoli and C. Zhao, *Adv. Energy Mater.*, 2021, 2003759.
- 150 A. Wang, H. Niu, X. Wang, X. Wan, L. Xie, Z. Zhang, J. Wang and Y. Guo, *J. Mater. Chem. A*, 2022, **10**, 13005–13012.
- 151 J. Chen, H. Li, C. Fan, Q. Meng, Y. Tang, X. Qiu, G. Fu and T. Ma, *Adv. Mater.*, 2020, **32**, 2003134.
- 152 Y. Kang, S. Wang, K. S. Hui, H. F. Li, F. Liang, X. L. Wu, Q. Zhang, W. Zhou, L. Chen, F. Chen and K. N. Hui, *Mater. Today Energy*, 2021, **20**, 100572.
- 153 Y. Wu, X. Qiu, F. Liang, Q. Zhang, A. Koo, Y. Dai, Y. Lei and X. Sun, *Appl. Catal., B*, 2019, **241**, 407–414.
- 154 J. Zhu, T. Qu, F. Su, Y. Wu, Y. Kang, K. Chen, Y. Yao, W. Ma, B. Yang, Y. Dai, F. Liang and D. Xue, *Dalton Trans.*, 2020, **49**, 1811–1821.
- 155 H. Gao, S. Zhu, Y. Kang, D. A. Dinh, K. S. Hui, F. Bin, X. Fan, F. Chen, A. Mahmood, J. Geng, W.-C. M. Cheong and K. N. Hui, *ACS Appl. Energy Mater.*, 2022, **5**, 1662–1671.
- 156 Y. Liu, X. Chi, Q. Han, Y. Du, J. Huang, X. Lin and Y. Liu, *Nanoscale*, 2019, **11**, 5285–5294.
- 157 X. Yang, F. Su, M. Hou, D. Zhang, Y. Dai and F. Liang, *Dalton Trans.*, 2021, **50**, 7041–7047.
- 158 W. Y. Noh, E. M. Kim, K. Y. Kim, J. H. Kim, H. Y. Jeong, P. Sharma, G. Lee, J.-W. Jang, S. H. Joo and J. S. Lee, *J. Mater. Chem. A*, 2020, **8**, 18891–18902.
- 159 N. Li, Y. Yin, F. Meng, Q. Zhang, J. Yan and Q. Jiang, *ACS Catal.*, 2017, **7**, 7688–7694.
- 160 M. Kim, H. Ju and J. Kim, *Dalton Trans.*, 2018, **47**, 15217–15225.
- 161 M. Kim, H. Ju and J. Kim, *J. Mater. Chem. A*, 2018, **6**, 8523–8530.
- 162 M. Kim, H. Ju and J. Kim, *Appl. Catal., B*, 2019, **245**, 29–39.
- 163 L. Sharma, R. Gond, B. Senthilkumar, A. Roy and P. Barpanda, *ACS Catal.*, 2020, **10**, 43–50.
- 164 B. Senthilkumar, A. Irshad and P. Barpanda, *ACS Appl. Mater. Interfaces*, 2019, **11**, 33811–33818.
- 165 B. Senthilkumar, Z. Khan, S. Park, I. Seo, H. Ko and Y. Kim, *J. Power Sources*, 2016, **311**, 29–34.
- 166 J. Shamblyn, M. Feygenzon, J. Neufeind, C. L. Tracy, F. Zhang, S. Finkeldei, D. Bosbach, H. Zhou, R. C. Ewing and M. Lang, *Nat. Mater.*, 2016, **15**, 507–511.
- 167 J. Park, M. Risch, G. Nam, M. Park, T. J. Shin, S. Park, M. G. Kim, Y. Shao-Horn and J. Cho, *Energy Environ. Sci.*, 2017, **10**, 129–136.



- 168 J. Parrondo, M. George, C. Capuano, K. E. Ayers and V. Ramani, *J. Mater. Chem. A*, 2015, **3**, 10819–10828.
- 169 H. Kim, J. Park, I. Park, K. Jin, S. E. Jerng, S. H. Kim, K. T. Nam and K. Kang, *Nat. Commun.*, 2015, **6**, 8253.
- 170 R. Gond, K. Sada, B. Senthikumar and P. Barpanda, *ChemElectroChem*, 2018, **5**, 153–158.
- 171 C. Delacourt, P. Poizot, J.-M. Tarascon and C. Masquelier, *Nat. Mater.*, 2005, **4**, 254–260.
- 172 C. Masquelier and L. Croguennec, *Chem. Rev.*, 2013, **113**, 6552–6591.
- 173 E. Doustkhah, H. Mohtasham, M. Farajzadeh, S. Rostamnia, Y. Wang, H. Arandiyani and M. H. N. Assadi, *Microporous Mesoporous Mater.*, 2020, **293**, 109832.
- 174 H. Arandiyani, H. Chang, C. Liu, Y. Peng and J. Li, *J. Mol. Catal. A: Chem.*, 2013, **378**, 299–306.
- 175 H. Arandiyani, K. Kani, Y. Wang, B. Jiang, J. Kim, M. Yoshino, M. Rezaei, A. E. Rowan, H. Dai and Y. Yamauchi, *ACS Appl. Mater. Interfaces*, 2018, **10**, 24963–24968.
- 176 Y. Wang, H. Arandiyani, S. A. Bartlett, A. Trunschke, H. Sun, J. Scott, A. F. Lee, K. Wilson, T. Maschmeyer, R. Schlögl and R. Amal, *Appl. Catal., B*, 2020, **277**, 119029.
- 177 C. Jia, S. Li, Y. Zhao, R. K. Hocking, W. Ren, X. Chen, Z. Su, W. Yang, Y. Wang, S. Zheng, F. Pan and C. Zhao, *Adv. Funct. Mater.*, 2021, **31**, 2107072.
- 178 N. Mozhzhukhina, L. P. Méndez De Leo and E. J. Calvo, *J. Phys. Chem. C*, 2013, **117**, 18375–18380.
- 179 J. P. Vivek, N. Berry, G. Papageorgiou, R. J. Nichols and L. J. Hardwick, *J. Am. Chem. Soc.*, 2016, **138**, 3745–3751.
- 180 N. Mozhzhukhina, A. Y. Tesio, L. P. M. De Leo and E. J. Calvo, *J. Electrochem. Soc.*, 2017, **164**, A518–A523.
- 181 R. Cao, E. D. Walter, W. Xu, E. N. Nasybulin, P. Bhattacharya, M. E. Bowden, M. H. Engelhard and J.-G. Zhang, *ChemSusChem*, 2014, **7**, 2436–2440.
- 182 J. Kim, H. Park, B. Lee, W. M. Seong, H.-D. Lim, Y. Bae, H. Kim, W. K. Kim, K. H. Ryu and K. Kang, *Nat. Commun.*, 2016, **7**, 10670.
- 183 D. S. Shin, N. Doddapaneni and S. M. Park, *Inorg. Chem.*, 1992, **31**, 4060–4064.
- 184 I. Landa-Medrano, M. Olivares-Marín, R. Pinedo, I. Ruiz de Larramendi, T. Rojo and D. Tonti, *Electrochem. Commun.*, 2015, **59**, 24–27.
- 185 Q. Yu and S. Ye, *J. Phys. Chem. C*, 2015, **119**, 12236–12250.
- 186 T. Yuan, L. Le Thi Ngoc, J. van Nieuwkastele, M. Odijk, A. van den Berg, H. Permentier, R. Bischoff and E. T. Carlen, *Anal. Chem.*, 2015, **87**, 2588–2592.
- 187 Z. Peng, S. A. Freunberger, L. J. Hardwick, Y. Chen, V. Giordani, F. Bardé, P. Novák, D. Graham, J.-M. Tarascon and P. G. Bruce, *Angew. Chem., Int. Ed.*, 2011, **50**, 6351–6355.
- 188 L. Johnson, C. Li, Z. Liu, Y. Chen, S. A. Freunberger, P. C. Ashok, B. B. Praveen, K. Dholakia, J.-M. Tarascon and P. G. Bruce, *Nat. Chem.*, 2014, **6**, 1091–1099.
- 189 I. M. Aldous and L. J. Hardwick, *Angew. Chem., Int. Ed.*, 2016, **55**, 8254–8257.
- 190 J. Wang, Y. Zhang, L. Guo, E. Wang and Z. Peng, *Angew. Chem., Int. Ed.*, 2016, **55**, 5201–5205.
- 191 J. Staszak-Jirkovský, R. Subbaraman, D. Strmcnik, K. L. Harrison, C. E. Diesendruck, R. Assary, O. Frank, L. Kobr, G. K. H. Wiberg, B. Genorio, J. G. Connell, P. P. Lopes, V. R. Stamenkovic, L. Curtiss, J. S. Moore, K. R. Zavadil and N. M. Markovic, *ACS Catal.*, 2015, **5**, 6600–6607.
- 192 J. T. Frith, A. E. Russell, N. Garcia-Araez and J. R. Owen, *Electrochem. Commun.*, 2014, **46**, 33–35.
- 193 T. A. Galloway and L. J. Hardwick, *J. Phys. Chem. Lett.*, 2016, **7**, 2119–2124.

