

Cite this: *Nanoscale Adv.*, 2025, 7, 3358

# Magnetically recoverable $\text{MFe}_{12}\text{O}_{19}$ nanoparticles as efficient and environmentally benign catalysts for gram-scale selective oxidation of olefins

Mouhsine Laayati,<sup>abe</sup> Ayoub Abdelkader Mekkaoui,<sup>id</sup> \*<sup>b</sup> Ahsen Sare Yalin,<sup>c</sup>  
Abdelhamid El Boubekri,<sup>d</sup> Mohammed Sajjeddine,<sup>d</sup> Larbi El Firdoussi,<sup>b</sup>  
Antonia Neels,<sup>id</sup> \*<sup>e</sup> Önder Metin,<sup>id</sup> \*<sup>cf</sup> and Soufiane El Houssame,<sup>id</sup> \*<sup>a</sup>

Catalytic oxidation is an efficient route for synthesizing oxygenated compounds such as epoxides and aldehydes. However, developing cost-effective, environmentally friendly and selective gram-scale catalysts, in full agreement with circular economy and green chemistry principles, remains a significant challenge. Herein, we report on  $\text{MFe}_{12}\text{O}_{19}$  magnetic nanoparticles (MNPs) as a novel, magnetically recoverable and selective catalyst for the oxidation of olefins. Three different  $\text{MFe}_{12}\text{O}_{19}$  ( $\text{M} = \text{Cu}, \text{Sn}$  and  $\text{Sr}$ ) MNPs were synthesized using the coprecipitation method and characterized by XRD, FTIR, Raman, XPS, SEM-EDX, TEM, BET, zeta potential and  $^{57}\text{Fe}$  Mössbauer spectroscopy. XRD analysis demonstrates that the patterns of  $\text{SnFe}_{12}\text{O}_{19}$  and  $\text{CuFe}_{12}\text{O}_{19}$  are totally different from those of the magnetoplumbite hexaferrite structure due to the confirmed coexistence by Rietveld refinements of  $\text{SnO}_2\text{--Fe}_2\text{O}_3$  and  $\text{CuFe}_2\text{O}_4\text{--Fe}_2\text{O}_3$  as composite structures, respectively. In good agreement, Raman studies exclusively confirms the coexistence of  $\text{MO}_x\text{--Fe}_2\text{O}_3$  as a composite structure in  $\text{MFe}_{12}\text{O}_{19}$ , due to the presence of  $\alpha\text{--Fe}_2\text{O}_3$  and  $\gamma\text{--Fe}_2\text{O}_3$  as intermediate phases during the formation process of the hexaferrite structure. Moreover, the XPS and Mössbauer results are consistent with the experimental evidence and spectroscopic characterizations. Subsequently, the catalytic activity of the as-synthesized MNPs was evaluated for the oxidation of styrene as a model olefinic substrate. Among the as-prepared  $\text{MFe}_{12}\text{O}_{19}$  MNPs, the composite structure  $\text{CuFe}_2\text{O}_4\text{--Fe}_2\text{O}_3$  in  $\text{CuFe}_{12}\text{O}_{19}$  effectively enhances catalytic activity, selectivity and reusability due to the synergistic catalytic effect within a single magnetically recoverable nanostructure. Overall,  $\text{MFe}_{12}\text{O}_{19}$  MNPs present a facile and greener approach using magnetically recyclable hexaferrites for selective catalytic oxidation reactions.

Received 18th February 2025  
Accepted 25th March 2025

DOI: 10.1039/d5na00167f

rsc.li/nanoscale-advances

## 1. Introduction

Styrene oxide and benzaldehyde are important organic intermediates widely used in the industrial manufacture of fragrances, pharmaceuticals, and organic synthesis.<sup>1–4</sup> Hence, the oxidation of olefins has been widely regarded as one of the

most important routes to accessing epoxides and aldehydes.<sup>5</sup> To date, both homogeneous and heterogeneous catalysts have been extensively reported for the oxidation of olefins.<sup>6–15</sup> Catalysis plays an important role in green chemistry by enabling less polluting chemical processes and providing sustainable pathways to synthesize desired products.<sup>16</sup> Heterogeneous catalysts are widely preferred over homogeneous ones owing to their recyclability and atom economy, which contribute to sustainability by reducing time- and energy-consuming catalytic processes in alignment with the circular economy. Particular attention has been given to the development of selective heterogeneous catalysts for the oxidation of styrene to benzaldehyde or styrene oxide. Magnetic nanoparticles (MNPs) are especially attractive candidates for this reaction owing to their high activity, selectivity, and facile reusability.<sup>17</sup> Moreover, MNPs exhibit numerous advantageous properties, including a large surface-to-volume ratio, good crystallinity, excellent thermal stability and homogeneous composition as heterogeneous bulk catalysts, all of which contribute to their high catalytic performance.<sup>17–20</sup>

<sup>a</sup>Laboratoire des Sciences des Matériaux, Mathématiques et Environnement, Université Sultan Moulay Slimane, Faculté Polydisciplinaire de Khouribga, BP 145, Khouribga 25000, Morocco. E-mail: hous\_soufiane@hotmail.com

<sup>b</sup>Cadi Ayyad University, UCA, Faculté des Sciences Semlalia Marrakech, Département de Chimie, Laboratoire de Chimie Moléculaire, Equipe de Chimie de Coordination et de Catalyse, BP 2390, Marrakech 40001, Morocco. E-mail: mekk.ayoub@gmail.com; a.mekkaoui@uca.ac.ma

<sup>c</sup>Department of Chemistry, College of Sciences, Koç University, 34450 Istanbul, Turkey

<sup>d</sup>Laboratoire Génie Énergétique et Matériaux, Université Sultan Moulay Slimane, Faculté des Sciences et Techniques, BP 523, Béni Mellal 23000, Morocco

<sup>e</sup>Center for X-Ray Analytics, Empa - Swiss Federal Laboratories for Materials Science and Technology, Überlandstrasse 129, 8600 Dübendorf, Switzerland

<sup>f</sup>Koç University Surface Science and Technology Center (KUYTAM), Koç University, Istanbul 34450, Turkey



M-type hexaferrite, with a chemical formula of  $\text{MFe}_{12}\text{O}_{19}$ , is a class of promising chemically and thermally stable magnetic materials for a wide range of applications. Regarding their high magneto-crystalline anisotropy with a single easy magnetization axis, they are classified as hard magnets with high coercivity.<sup>21</sup> They have been widely used as permanent magnets, recording media, photocatalysts and components in microwave, telecommunication, higher-frequency, and magneto-optical devices.<sup>22–29</sup> Moreover, special attention has been given to magnetic materials based on barium, strontium, palladium and lead with unique properties.<sup>30</sup> Previously, Ansari *et al.* reported on the synthesis of  $\text{CuFe}_{12}\text{O}_{19}$  nanostructures by using sol-gel auto-combustion method and its magnetic properties.<sup>31</sup> Recently,  $\text{SnFe}_{12}\text{O}_{19}$  nanostructures were synthesized through ultrasonic irradiation and utilized in an environmental application.<sup>32</sup> Based on the current understanding, the XRD patterns of these reported structures  $\text{MFe}_{12}\text{O}_{19}$  ( $\text{M} = \text{Cu}$  or  $\text{Sn}$ ) are not yet confirmed, and they are totally different from those of the magnetoplumbite hexaferrite structure. Hence, there is a lack of advanced spectroscopic investigations in the reported literature to accurately assess the structural properties of such  $\text{MFe}_{12}\text{O}_{19}$  compounds. For this reason,  $\text{Cu}$  and  $\text{Sn}$  have been selected to study the obtained  $\text{MFe}_{12}\text{O}_{19}$  compounds and compare them with the  $\text{SrFe}_{12}\text{O}_{19}$  M-type hexaferrite.

In the last decades, owing to their magnetic properties, M-type hexaferrites have attracted the attention of scientists in various fields of catalytic applications. Recently, the  $\text{SrFe}_{12}\text{O}_{19}$  M-type hexaferrite was reported as high catalytically active MNPs for the improvement of the catalytic epoxide ring-opening reaction with amines, as pristine<sup>33</sup> or in hybrid graphene-derived nanocomposites,<sup>34</sup> as well as in the synthesis of 2-amino-4,6-diphenylnicotinonitrile<sup>35</sup> and 1,5-benzodiazepine derivatives.<sup>36</sup> However, the presumed  $\text{MFe}_{12}\text{O}_{19}$  ( $\text{M} = \text{Cu}$  or  $\text{Sn}$ ) nanoparticles have only been reported in a few studies. According to the literature,  $\text{CuFe}_{12}\text{O}_{19}$  MNPs and the grafted ones on CNT have only been reported for photocatalytic elimination of water contamination.<sup>37,38</sup> To the best of our knowledge,  $\text{CuFe}_{12}\text{O}_{19}$  and  $\text{SnFe}_{12}\text{O}_{19}$  nanoparticles have not yet been used as heterogeneous catalysts for any application. In this regard, the growing potential of hexaferrite MNPs in catalysis motivates further study of their catalytic activity in alignment with green chemistry principles and circular economy.

In this study, we focus on the development of novel hexaferrite nanostructures as magnetically recoverable nanoparticles (MNPs) for catalytic applications, leveraging their magnetic properties, stability and high specific surface area. Various chemical methods, including sol-gel,<sup>31,39,40</sup> salt melting process,<sup>41</sup> sonochemical<sup>32,42</sup> and coprecipitation,<sup>33,43</sup> have previously been employed for the synthesis of M-type hexaferrites. Among these, the chemical coprecipitation method stands out due to its simplicity and precision in controlling the grain size, making it an excellent approach for preparing magnetic oxide nanoparticles. Herein, we present the synthesis of  $\text{CuFe}_{12}\text{O}_{19}$ ,  $\text{SnFe}_{12}\text{O}_{19}$  and  $\text{SrFe}_{12}\text{O}_{19}$  NPs using a reproducible coprecipitation method. To the best of our knowledge, this is the first study to evaluate the catalytic performance of as-

prepared  $\text{MFe}_{12}\text{O}_{19}$  NPs in the oxidation of styrene derivatives, chosen as model substrates for olefin oxidation.

## 2. Experimental

### 2.1. Materials

All reagents and solvents were obtained from commercial suppliers (Aldrich and Acros), and used directly without further purification. As-synthesized nanoparticles (NPs) were characterized by X'Pert MPD Powder instrument from Malvern Panalytical with  $\text{Cu K}\alpha$  radiation ( $\lambda_{\text{Cu}} = 1.5406 \text{ \AA}$ ). A Bruker vertex 70 DTGSFTIR spectrophotometer was used to record the stretching vibrational frequencies of NPs in the range of  $400\text{--}4000 \text{ cm}^{-1}$ . X-ray photoelectron spectra (XPS) were obtained using a Thermo Scientific K-Alpha spectrometer using an aluminum anode ( $\text{Al K}\alpha_{1/2}$  1468.3 eV). The binding energies were calibrated by referencing the C 1s signal at 284.4 eV. Morphology and topology of the materials were characterized by using a scanning electron microscope (SEM) (FEI, Quanta FEG 450). Transmission Mössbauer spectra were collected by using a conventional constant acceleration spectrometer with a 25 mCi source  $^{57}\text{Co}$  sealed in a Rh matrix at room temperature. In this configuration, the  $\gamma$ -ray direction is perpendicular to the powder plane. *NORMOS DIST* program was used to interpret the experimental spectra.<sup>44</sup> All isomer shift values are reported with respect to that of the  $\alpha$ -iron foil at room temperature. Transmission electron microscope (TEM) images were recorded on a 120 kV Hitachi HT7800 TEM instrument with EXALENS module capable of working at high-resolution (HR) mode in the magnification range of  $10\text{--}600\times$ . BET measurements were conducted using the Micromeritics Tristar II automated gas sorption system. The zeta potential was measured using a Malvern Panalytical Zetasizer, after dispersing 0.1 g of nanopowders in 3 ml of solvent (acetonitrile; acetone or deionized water). Aliquot samples from the reaction mixture were monitored by gas chromatography (GC, Shimadzu) equipped with a flame ionization detector and nitrogen as the carrier gas. The GC conditions for the BP capillary columns ( $25 \text{ m} \times 0.25 \text{ mm}$ , SGE) were set as follows: injector temperature at  $250 \text{ }^{\circ}\text{C}$ ; detector temperature at  $250 \text{ }^{\circ}\text{C}$  and oven temperature initially set at  $70 \text{ }^{\circ}\text{C}$  for 5 min, followed by a ramp of  $3 \text{ }^{\circ}\text{C min}^{-1}$  until reaching  $250 \text{ }^{\circ}\text{C}$  for 30 min. The column pressure was maintained at 20 kPa with a flow rate of  $6.3 \text{ ml min}^{-1}$ , linear velocity of  $53.1 \text{ cm s}^{-1}$  and total flow of  $138 \text{ ml min}^{-1}$ . The products were confirmed by injecting the reaction mixture into an ISQ LT single quadrupole mass spectrometer, operating in positive EI mode, and scanning a mass range of 50 to 400  $m/z$ .

### 2.2. Synthesis of the $\text{MFe}_{12}\text{O}_{19}$ nanoparticles

The magnetic  $\text{MFe}_{12}\text{O}_{19}$  ( $\text{M} = \text{Sr}$ ;  $\text{Cu}$ ; or  $\text{Sn}$ ) nanoparticles were synthesized by following a coprecipitation protocol.<sup>33,34</sup> In a typical synthesis protocol, stoichiometric quantities of metal chlorides ( $\text{SrCl}_2 \cdot 6\text{H}_2\text{O}$ ;  $\text{CuCl}_2$ ;  $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$ ;  $\text{FeCl}_3$ ) were individually dissolved in 30 ml of deionized water to form homogeneous solutions. These solutions were then mixed and stirred for 30 min at  $80 \text{ }^{\circ}\text{C}$ . Next, pH of the reaction mixture was



adjusted to 11–12 *via* dropwise addition of NaOH (1.5 M) under continuous stirring for 1.5–2 h at 80 °C, ensuring the homogeneity of the mixture. The precipitated  $\text{CuFe}_{12}\text{O}_{19}$  and  $\text{SnFe}_{12}\text{O}_{19}$  nanopowders were separated magnetically. In contrast,  $\text{SnFe}_{12}\text{O}_{19}$  was separated *via* centrifugation due to the lack of its magnetization. The prepared  $\text{MFe}_{12}\text{O}_{19}$  nanopowders were washed several times with deionized water to remove the excess salt and dried at 80 °C overnight. The obtained nanopowders were calcined at 900 °C for 8 h to obtain the pure hexaferrites.

### 2.3. Catalytic studies

**2.3.1. Selective synthesis of epoxide or aldehyde derivatives.** In a typical reaction, the synthesis of epoxide derivatives was performed by combining olefin (1.92 mmol), *t*BHP 70 wt% (3 eq.),  $\text{CuFe}_{12}\text{O}_{19}$  ( $1.92 \times 10^{-2}$  mmol, %mol ( $\text{CuFe}_{12}\text{O}_{19}$ ) = 1%) and 2 ml of acetonitrile as solvent. The mixture was then placed in a 50 ml Rotaflo tube and stirred at 60 °C for 24 h. The progress of the reaction was monitored by GC using dodecane as the internal standard. At the end of the reaction, the catalyst was recovered by an external magnetic field, washed with deionized water and acetone, and dried in an oven at 80 °C for 6 h before reuse. For the synthesis of the aldehyde derivatives, the oxidation reaction was carried out in the presence of  $\text{H}_2\text{O}_2$ , 30 wt% (3 eq.), in 2 ml of acetone as the solvent at 80 °C for 24 h.

## 3. Results and discussion

### 3.1. $\text{MFe}_{12}\text{O}_{19}$ characterization

The structures of the as-synthesized  $\text{MFe}_{12}\text{O}_{19}$  NPs ( $\text{M} = \text{Cu}$ ,  $\text{Sn}$  and  $\text{Sr}$ ) were first characterized by X-ray diffraction (XRD) (Fig. 1). While all the diffraction lines of  $\text{CuFe}_{12}\text{O}_{19}$  MNPs match the reported ones in the literature,<sup>31</sup> the diffraction patterns of  $\text{CuFe}_2\text{O}_4$  (JCPDS: 77-0010) and  $\text{Fe}_2\text{O}_3$  (JCPDS: 24-0072) reveal the coexistence of  $\text{CuFe}_2\text{O}_4$ – $\text{Fe}_2\text{O}_3$  as a composite structure in the as-synthesized  $\text{CuFe}_{12}\text{O}_{19}$  MNPs. Accordingly, while the XRD pattern of  $\text{SnFe}_{12}\text{O}_{19}$  also matched the reported literature,<sup>32</sup> the crystalline phases of  $\text{SnO}_2$  (JCPDS: 72-1147) and  $\text{Fe}_2\text{O}_3$  (JCPDS: 24-0072) indicate the coexistence of  $\text{SnO}_2$ – $\text{Fe}_2\text{O}_3$  as possible composite structure. However, the XRD pattern of the as-prepared  $\text{SrFe}_{12}\text{O}_{19}$  presents a very similar diffraction pattern

as reported for the magnetoplumbite hexaferrite structure.<sup>34</sup> In addition, the  $\text{SrFe}_{12}\text{O}_{19}$  crystal phase clearly matches well with the known strontium hexaferrite crystal phase (JCPDS: 33-1340). No obvious peaks of metal oxides ( $\text{SrO}$  and  $\text{Fe}_2\text{O}_3$ ) are observed, clearly indicating only the presence of the pure  $\text{SrFe}_{12}\text{O}_{19}$  hexaferrite structure.

Based on the XRD results, Rietveld refinement was carried out to accurately assess the observed structural differences of both compounds  $\text{CuFe}_{12}\text{O}_{19}$  and  $\text{SnFe}_{12}\text{O}_{19}$  compared to the magnetoplumbite M-type hexaferrite structure of the  $\text{SrFe}_{12}\text{O}_{19}$  MNPs. The recorded and Rietveld refined XRD patterns of the as-presumed prepared hexaferrites are displayed in Fig. 2. Clearly, in  $\text{SnFe}_{12}\text{O}_{19}$  and  $\text{CuFe}_{12}\text{O}_{19}$ , the refined XRD patterns exhibit a combination of two distinct parent phases. The refinement confirmed that  $\text{CuFe}_{12}\text{O}_{19}$  exhibits a spinel structure with the  $Fd\bar{3}m$  space group and hematite ( $\text{Fe}_2\text{O}_3$ ) as the main phase (73.5%). However, the  $\text{SnFe}_{12}\text{O}_{19}$  XRD pattern presents the hematite phase (92.5%) as the major component and the minor crystalline phase of  $\text{SnO}_2$  (7.5%). Table 1 presents the fitting parameters and crystallite sizes ( $D$ ), using the most intense and single indexed reflection of all phases, as found in the as-prepared  $\text{MFe}_{12}\text{O}_{19}$  NPs.

The Rietveld refinement study reveals good agreement between the experimental and calculated patterns. Moreover, based on what is currently known, we can assume that the structural properties of both  $\text{CuFe}_{12}\text{O}_{19}$  and  $\text{SnFe}_{12}\text{O}_{19}$  have never been reported with such experimental proof, which may explain the XRD outcomes compared to the magnetoplumbite structure due to the coexistence of  $\text{SnO}_2$ – $\text{Fe}_2\text{O}_3$  and  $\text{CuFe}_2\text{O}_4$ – $\text{Fe}_2\text{O}_3$ . Consequently, we can assume that they are not isostructural with the  $\text{SrFe}_{12}\text{O}_{19}$  M-type hexaferrite.

The FTIR spectra of all synthesized  $\text{MFe}_{12}\text{O}_{19}$  NPs present the characteristic peaks of metal–oxygen stretching vibrations at around 460–630  $\text{cm}^{-1}$  (Fig. 3).<sup>34</sup> However, the peaks around 3400 and 1600  $\text{cm}^{-1}$  are attributed to the stretching and the bending vibrations, respectively, of the adsorbed water on the  $\text{MFe}_{12}\text{O}_{19}$  NPs.<sup>32,38</sup>

Fig. 4 shows the Raman spectra of the obtained  $\text{MFe}_{12}\text{O}_{19}$  NPs. The Raman shifts observed for  $\text{SrFe}_{12}\text{O}_{19}$  are attributed to the  $\text{A}_{1g}$ ,  $\text{E}_{1g}$ , and  $\text{E}_{2g}$  modes. The tetrahedral 4f1 and bipyrmidal 2b sites of  $\text{SrFe}_{12}\text{O}_{19}$  exhibit  $\text{A}_{1g}$  vibrations of Fe–O bonds at 724 and 690  $\text{cm}^{-1}$ , respectively. Meanwhile, the octahedral 4f2, 2a and 12k sites exhibit the same  $\text{A}_{1g}$  vibrations at 620 and 479  $\text{cm}^{-1}$ , respectively. At the octahedral 12k dominant site, the peak of the  $\text{A}_{1g}$  vibrations was detected at 407  $\text{cm}^{-1}$ . The band at 347  $\text{cm}^{-1}$  is attributed to an octahedra mode mix with  $\text{A}_{1g}$  and  $\text{E}_{1g}$  symmetries. While the  $\text{E}_{1g}$  vibrations of the entire spinel block are shown at 185  $\text{cm}^{-1}$ , the  $\text{E}_{1g}$  vibration modes are also seen at 295 and 225  $\text{cm}^{-1}$ . The bands at 534 and 432  $\text{cm}^{-1}$  were both attributed to  $\text{E}_{2g}$  modes.<sup>45,46</sup> On the other hand, the Raman spectrum of  $\text{SnFe}_{12}\text{O}_{19}$  reveals three Raman active modes (Fig. 4). While the observed peaks at 222 and 497  $\text{cm}^{-1}$  are both attributed to  $\text{A}_{1g}$ , the remaining four peaks at 243, 284, 407, and 609  $\text{cm}^{-1}$  may be assigned to the  $\text{E}_g$  mode of  $\alpha$ - $\text{Fe}_2\text{O}_3$  NPs.<sup>47</sup> However, the peaks at 499 and 701  $\text{cm}^{-1}$  are assigned to the  $\text{E}_g$  and  $\text{A}_{2u}$  active modes of  $\text{SnO}_2$ .<sup>47</sup> In addition, the Raman spectrum of  $\text{CuFe}_{12}\text{O}_{19}$  reveals peaks at

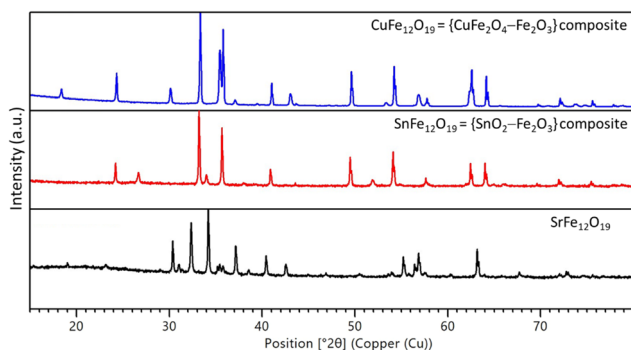


Fig. 1 XRD patterns of  $\text{CuFe}_{12}\text{O}_{19}$ ,  $\text{SnFe}_{12}\text{O}_{19}$  and  $\text{SrFe}_{12}\text{O}_{19}$ .



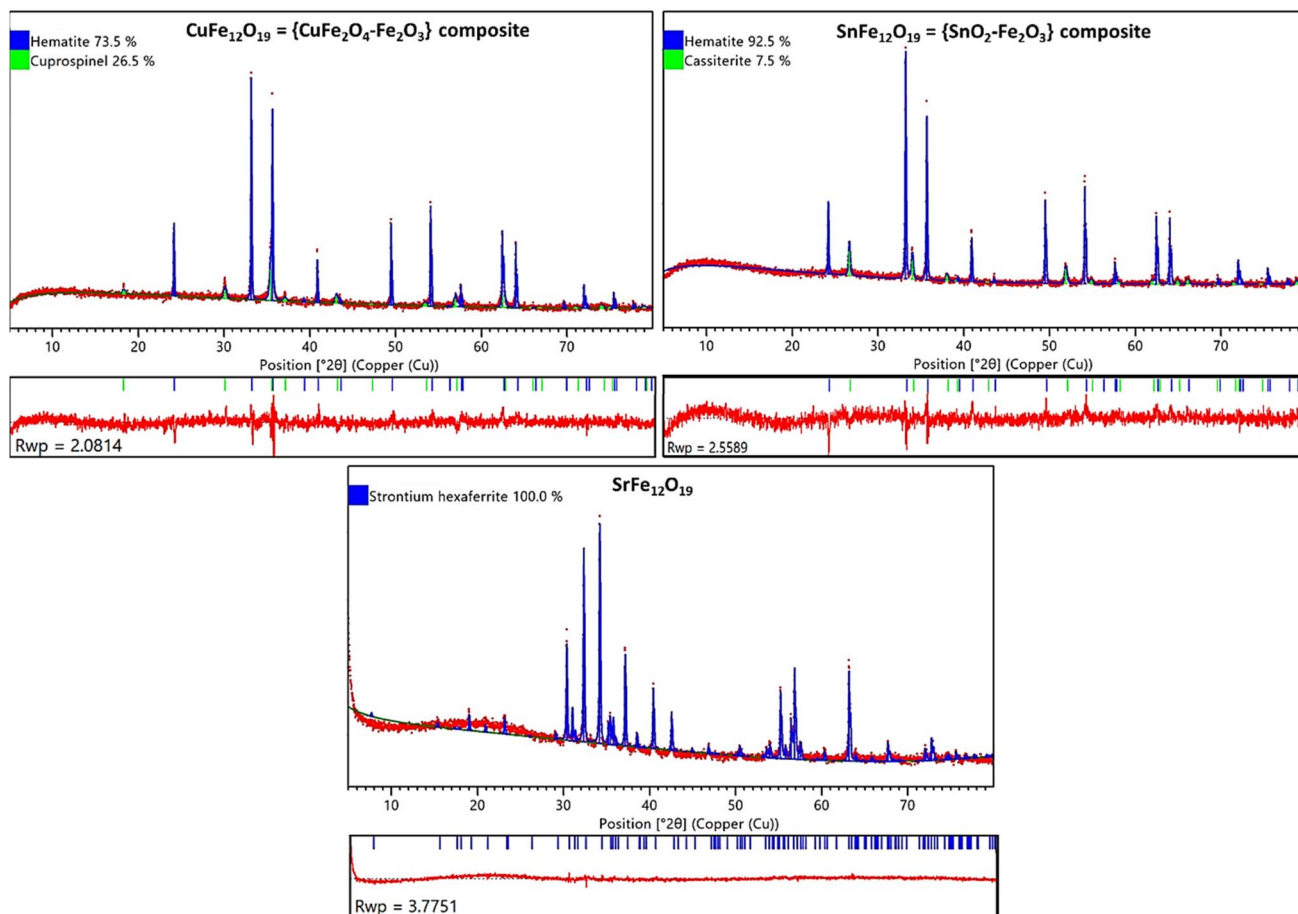


Fig. 2 Rietveld refinement of  $\text{CuFe}_{12}\text{O}_{19}$ ,  $\text{SnFe}_{12}\text{O}_{19}$  and  $\text{SrFe}_{12}\text{O}_{19}$ .

Table 1 Refined parameters of the XRD data for  $\text{MFe}_{12}\text{O}_{19}$  ( $\text{M} = \text{Cu}, \text{Sn}$  and  $\text{Sr}$ )

|                       | $\text{CuFe}_{12}\text{O}_{19} = \{\text{CuFe}_2\text{O}_4\text{-Fe}_2\text{O}_3\}$ |                         | $\text{SnFe}_{12}\text{O}_{19} = \{\text{SnO}_2\text{-Fe}_2\text{O}_3\}$ |                         | $\text{SrFe}_{12}\text{O}_{19}$ |
|-----------------------|-------------------------------------------------------------------------------------|-------------------------|--------------------------------------------------------------------------|-------------------------|---------------------------------|
| Phase                 | $\text{CuFe}_2\text{O}_4$                                                           | $\text{Fe}_2\text{O}_3$ | $\text{SnO}_2$                                                           | $\text{Fe}_2\text{O}_3$ | $\text{SrFe}_{12}\text{O}_{19}$ |
| Crystal structure     | Cubic spinel                                                                        | Hexagonal               | Tetragonal                                                               | Hexagonal               | Hexagonal                       |
| Group space           | $Fd\bar{3}m$                                                                        | $R\bar{3}c$             | $P4_2/mnm$                                                               | $R\bar{3}c$             | $P6_3/mmc$                      |
| Composition (%)       | 23.8                                                                                | 76.2                    | 7.5                                                                      | 92.5                    | 100                             |
| $a$ (Å)               | 8.42                                                                                | 5.033                   | 4.735                                                                    | 5.037                   | 5.882                           |
| $b$ (Å)               | 8.42                                                                                | 5.033                   | 4.735                                                                    | 5.037                   | 5.882                           |
| $c$ (Å)               | 8.42                                                                                | 13.741                  | 3.179                                                                    | 13.748                  | 23.051                          |
| $V$ (Å <sup>3</sup> ) | 598.69                                                                              | 301.53                  | 71.28                                                                    | 302.11                  | 690.85                          |
| $D$ (nm)              | 52.2                                                                                | 119.9                   | 37.4                                                                     | 160.1                   | 118.1                           |
| $R_{wp}$ (%)          | 8.09                                                                                |                         | 2.55                                                                     |                         | 3.77                            |
| $R_p$ (%)             | 4.61                                                                                |                         | 1.99                                                                     |                         | 2.62                            |
| $R_{exp}$ (%)         | 1.77                                                                                |                         | 1.93                                                                     |                         | 1.61                            |
| $\chi^2$              | 4.56                                                                                |                         | 1.32                                                                     |                         | 2.33                            |

226, 228, 409, 611, and 656  $\text{cm}^{-1}$ , matching the Raman active modes of  $\alpha\text{-Fe}_2\text{O}_3$  NPs.<sup>48</sup> Moreover, the broad peak around 1303  $\text{cm}^{-1}$  observed in all samples, with a noticeable differentiation in intensity, could be attributed to the Raman mode of  $\alpha\text{-Fe}_2\text{O}_3$ ,<sup>49</sup> which is in good agreement with the Rietveld study. Furthermore, the significant intensity of the  $\alpha\text{-Fe}_2\text{O}_3$

peak in the  $\text{SnFe}_{12}\text{O}_{19}$  structure may explain its lack of magnetization. In conclusion, the Raman spectra support the recorded and Rietveld refined XRD patterns, especially those of  $\text{CuFe}_{12}\text{O}_{19}$  and  $\text{SnFe}_{12}\text{O}_{19}$ , about a possible coexistence of  $\text{MO}_x\text{-Fe}_2\text{O}_3$  as a composite structure in the  $\text{MFe}_{12}\text{O}_{19}$  composition. Indeed, it was reported that  $\alpha\text{-Fe}_2\text{O}_3$  and  $\gamma\text{-Fe}_2\text{O}_3$  are

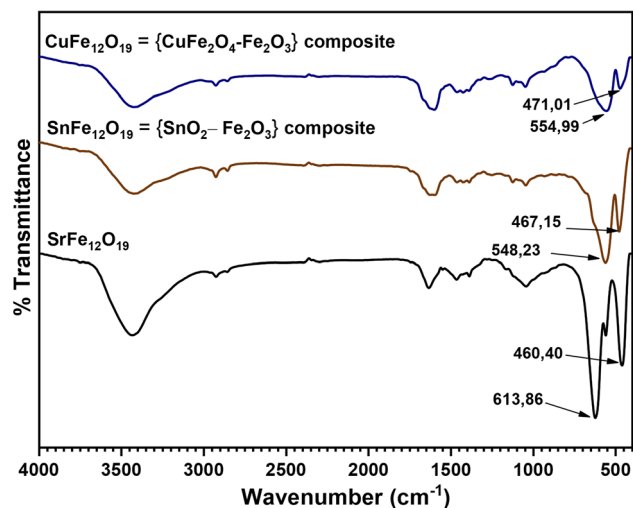


Fig. 3 FTIR spectra of  $\text{CuFe}_{12}\text{O}_{19}$ ,  $\text{SnFe}_{12}\text{O}_{19}$  and  $\text{SrFe}_{12}\text{O}_{19}$ .

intermediate phases during the formation process of the hexaferrite structure.<sup>49,50</sup> Moreover, their existence as intermediate phases supports the formation mechanism of  $\text{MFe}_{12}\text{O}_{19}$ . Specifically, the  $\gamma\text{-Fe}_2\text{O}_3$  phase is formed at low temperatures and incorporates cations into  $\text{MFe}_2\text{O}_4$ , which further reacts with  $\gamma\text{-Fe}_2\text{O}_3$  to form the  $\text{MFe}_{12}\text{O}_{19}$  phase. However, the  $\alpha\text{-Fe}_2\text{O}_3$  phase appears at higher temperatures, accompanied by the formation of the hexaferrite structure.

To understand the surface electronic and chemical configurations of the as-synthesized  $\text{MFe}_{12}\text{O}_{19}$  NPs, XPS analyses were carried out (Fig. 5). The chemical environment and the oxidation state of Cu, Sr, Sn and Fe were studied through the Cu 2p, Sr 3d, Sn 3p, Sn 3d and Fe 2p regions (Fig. 5b and c). All the expected elements, Cu, Sr, Sn, Fe and O, were detected in the XPS survey spectra of  $\text{MFe}_{12}\text{O}_{19}$  (Fig. 5a<sub>1</sub>–a<sub>3</sub>). The high-resolution XPS spectrum of the Cu 2p region in  $\text{CuFe}_{12}\text{O}_{19}$  shows the characteristic peaks of the Cu 2p<sub>3/2</sub> and Cu 2p<sub>1/2</sub> core-

levels at the binding energies (BEs) of 933.38 and 953.10 eV, as well as two additional peaks attributed to shakeup satellites at BEs of 940.49 and 961.78 eV (Fig. 5b<sub>1</sub>), respectively. Deconvolution of the Cu 2p XPS spectrum indicated the presence of  $\text{Cu}^{2+}$  of  $\text{CuFe}_2\text{O}_4$  in the as-synthesized  $\text{CuFe}_{12}\text{O}_{19}$ .<sup>51</sup> Meanwhile, the peaks located at BEs of 486.13 and 494.60 eV are attributed to 3d<sub>5/2</sub> and 3d<sub>3/2</sub> of  $\text{Sn}^{4+}$  (Fig. 5b<sub>3</sub>), respectively. In addition, the Sn 3d<sub>5/2</sub> and Sn 3d<sub>3/2</sub> core-levels are presented as a doublet with a spin-orbit split of  $\approx 8.5$  eV, which confirms the presence of  $\text{SnO}_2$  in the  $\text{SnFe}_{12}\text{O}_{19}$  composite structure.<sup>52</sup> However, the XPS spectrum of Sr 3d in  $\text{SrFe}_{12}\text{O}_{19}$  exhibits two peaks at BEs of 133.38 and 134.98 eV, attributed to the characteristic doublets of  $\text{Sr}^{2+}$  (Sr 3d<sub>5/2</sub> and Sr 3d<sub>3/2</sub>, respectively) (Fig. 5b<sub>3</sub>).<sup>53</sup>

The high-resolution XPS spectra of the Fe 2p regions of the  $\text{MFe}_{12}\text{O}_{19}$  NPs ( $\text{CuFe}_{12}\text{O}_{19}$ ,  $\text{SnFe}_{12}\text{O}_{19}$ , and  $\text{SrFe}_{12}\text{O}_{19}$ ) show similar two spin-orbit doublets at BEs of around 710 and 720 eV, corresponding to the Fe 2p<sub>3/2</sub> and Fe 2p<sub>1/2</sub> core-levels, as well as two additional peaks attributed to shakeup satellites at BEs of around 719 and 732 eV (Fig. 5c), respectively. Hence, the obtained 2p peaks and satellite peaks of Fe are in close agreement with the reported values for  $\text{Fe}^{3+}$  and the energy differences between the main 2p<sub>3/2</sub> and 2p<sub>1/2</sub> peaks ( $\approx 13.5$  eV), confirming the electronic state of  $\text{Fe}^{3+}$ .<sup>54</sup> Moreover, this electronic state in the as-synthesized  $\text{MFe}_{12}\text{O}_{19}$  NPs can be assigned to the contributions from  $\text{Fe}^{3+}$  in the octahedral and tetrahedral sites.<sup>54</sup> However, the noticeable difference in XPS spectrum of Fe in  $\text{SnFe}_{12}\text{O}_{19}$  is due to the appearance of Sn 3p<sub>3/2</sub> at the BE of 725.61 eV, which is in the same region as the shakeup satellite (at BE of 718.98 eV).<sup>55</sup> The deconvoluted spectra of O 1s show two peaks in the BE region of around 529–534 eV (Fig. 5d). While the peak at BE of around 530 eV is ascribed to the lattice oxygen in the metal–oxygen bond, the other one at BE of around 531.5 eV corresponds to the adsorbed  $\text{O}^-$  or  $\text{O}_2^{2-}$  species, which are associated with the intrinsic oxygen vacancies on the surface. However, the peak at BE of 530.04 eV for  $\text{SrFe}_{12}\text{O}_{19}$  is shifted to BE of around 529.5 eV in both  $\text{CuFe}_{12}\text{O}_{19}$  and

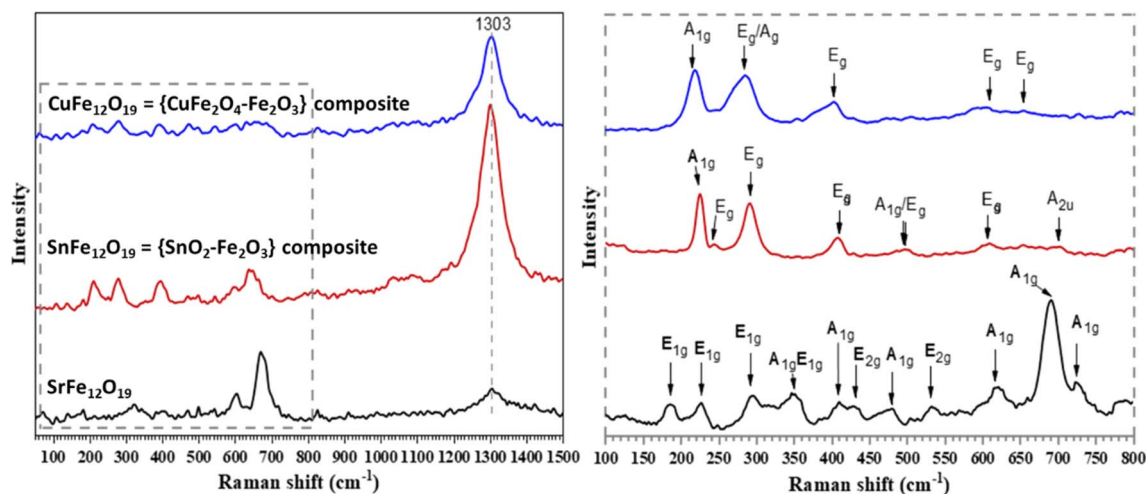


Fig. 4 Raman spectra of  $\text{CuFe}_{12}\text{O}_{19}$ ,  $\text{SnFe}_{12}\text{O}_{19}$  and  $\text{SrFe}_{12}\text{O}_{19}$ .

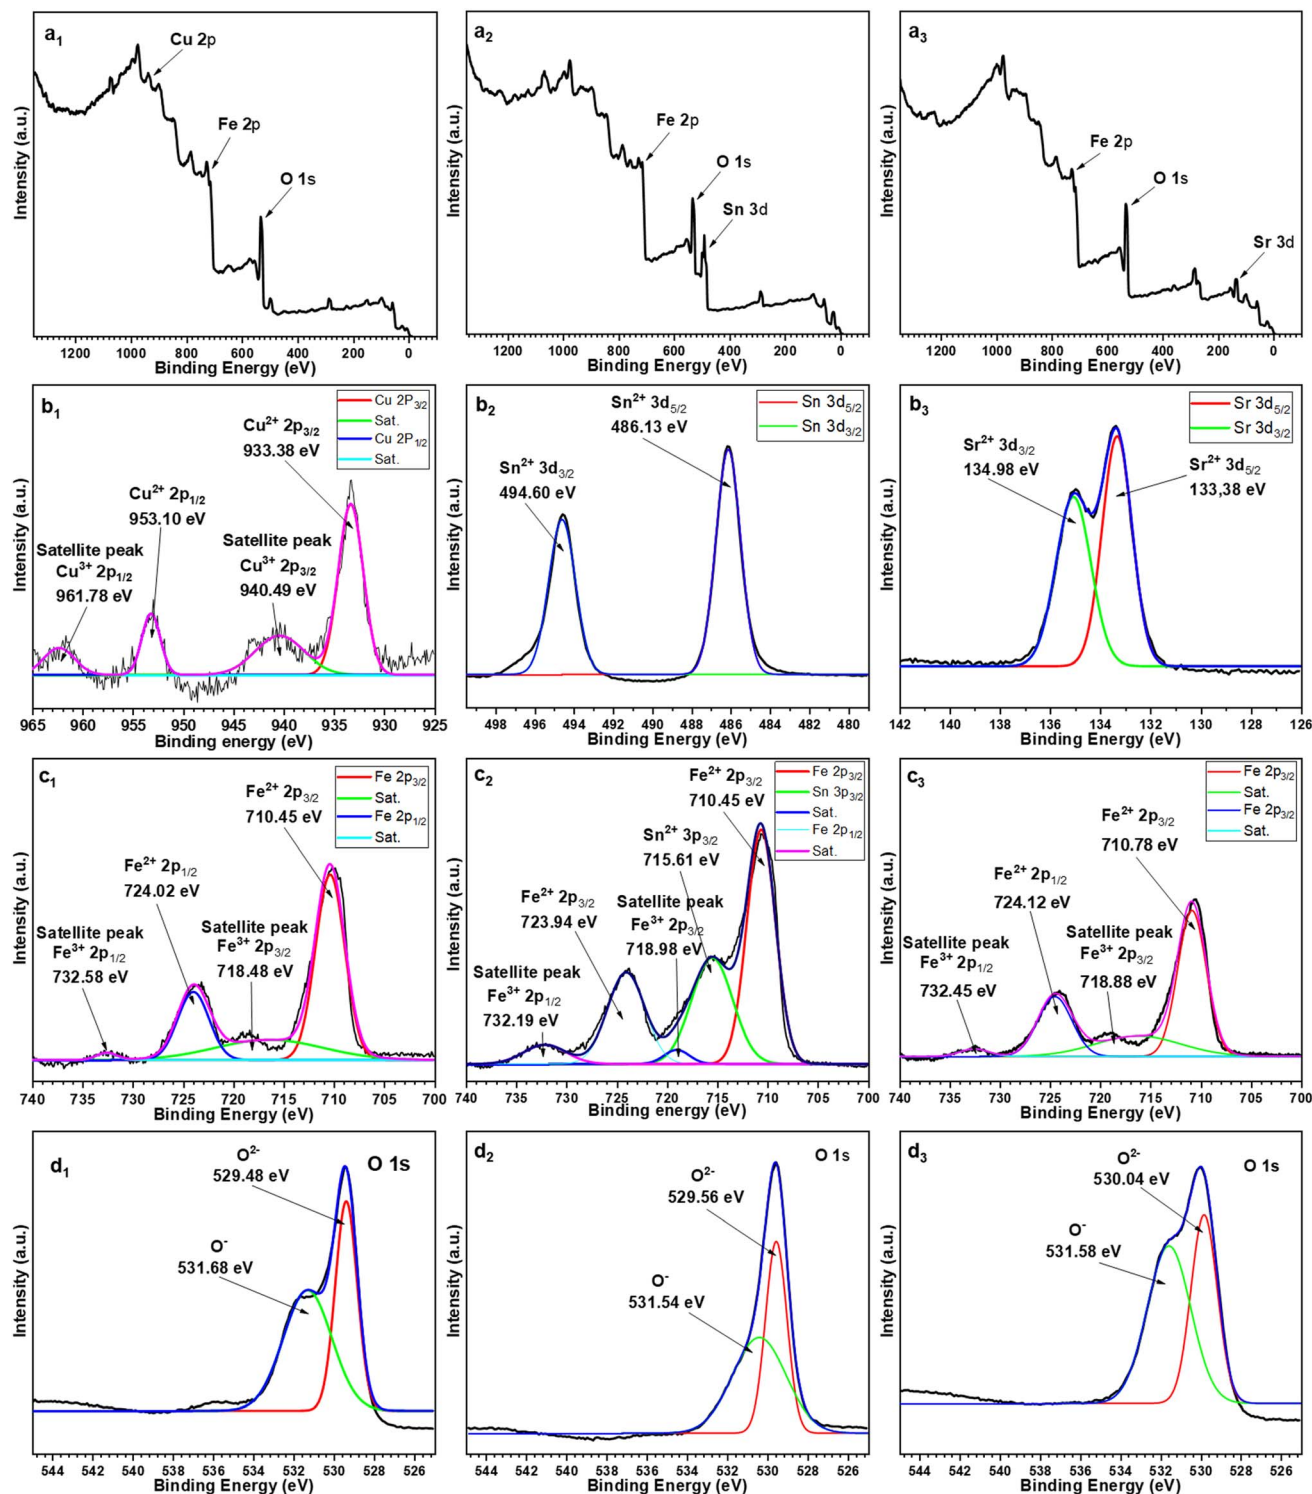


Fig. 5 XPS survey ( $a_1$ – $a_3$ ), high-resolution M ( $M = \text{Cu } 2p$ ,  $\text{Sr } 3d$ , and  $\text{Sn } 3d$ ) ( $b_1$ – $b_3$ ),  $\text{Fe } 2p$  ( $c_1$ – $c_3$ ) and  $\text{O } 1s$  spectra ( $d_1$ – $d_3$ ) of  $\text{CuFe}_{12}\text{O}_{19}$ ,  $\text{SnFe}_{12}\text{O}_{19}$ , and  $\text{SrFe}_{12}\text{O}_{19}$ , respectively.

$\text{SnFe}_{12}\text{O}_{19}$ , which could be attributed to the characteristic peak of  $\text{O}^{2-}$  in the hybrid oxide framework.<sup>56</sup>

<sup>57</sup>Fe Mössbauer spectroscopy is a highly effective technique for examining the oxidation state, local environment and magnetic characteristics of Fe atoms in the studied  $\text{MFe}_{12}\text{O}_{19}$

NPs. Fig. 6 shows the room temperature Mössbauer spectra of  $\text{CuFe}_{12}\text{O}_{19}$ ,  $\text{SnFe}_{12}\text{O}_{19}$  and  $\text{SrFe}_{12}\text{O}_{19}$  NPs. For  $\text{CuFe}_{12}\text{O}_{19}$ , the Mössbauer spectrum is well fitted using two sextets and one doublet, which confirms the presence of the  $\text{CuFe}_2\text{O}_4$ – $\text{Fe}_2\text{O}_3$  composite structure. While the two sextets are characteristic of

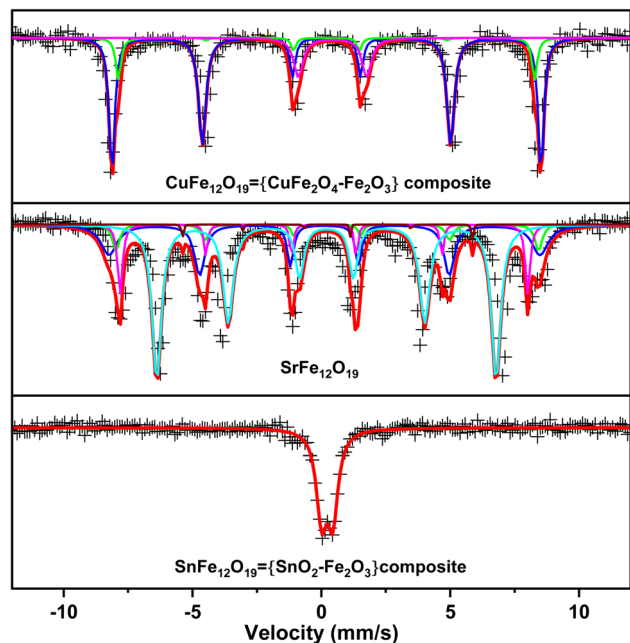


Fig. 6  $^{57}\text{Fe}$  Mössbauer spectra recorded at room temperature of  $\text{CuFe}_{12}\text{O}_{19}$ ,  $\text{SrFe}_{12}\text{O}_{19}$  and  $\text{SnFe}_{12}\text{O}_{19}$ .

the A and B sites of the  $\text{Fe}^{3+}$  ions present in the magnetically ordered structure of  $\text{CuFe}_2\text{O}_4$  at the tetrahedral and octahedral sites, the doublet is associated with  $\text{Fe}^{3+}$  ions in the paramagnetic state of  $\alpha\text{-Fe}_2\text{O}_3$ . However, the fitted experimental spectrum of  $\text{SrFe}_{12}\text{O}_{19}$  reveals a superposition of five magnetically split spectral components (sextets) characteristic of five different atomic environments around the Fe nuclei in the  $\text{SrFe}_{12}\text{O}_{19}$  M-type hexaferrite structure. Each one of these sextets is associated with a specific  $\text{Fe}^{3+}$  crystallographic site: one tetrahedral (4f1), one bipyramidal (2b) and three octahedral sites (12k, 4f2, and 2a). On the other hand, the spectrum of  $\text{SnFe}_{12}\text{O}_{19}$  shows a doublet characteristic of the paramagnetic iron atoms, confirming the lack of magnetization of the as-synthesized  $\text{SnFe}_{12}\text{O}_{19}$  nanoparticles due to the presence of the  $\text{SnO}_2\text{-Fe}_2\text{O}_3$  composite structure. Table 2 lists all of the hyperfine parameters, namely the percentage of area, isomer shift (IS), hyperfine field ( $B_{\text{hf}}$ ) and quadrupole splitting (QS). It

should also be noted that the Mössbauer results are consistent with the experimental evidence and the outcomes of the spectroscopic characterizations (XRD, FTIR, Raman and XPS).

To investigate the morphology and topology of the as-prepared  $\text{MFe}_{12}\text{O}_{19}$  nanoparticles, SEM images were recorded for all  $\text{MFe}_{12}\text{O}_{19}$  NPs (Fig. 7).  $\text{CuFe}_{12}\text{O}_{19}$  shows a uniform nanostructure with a homogeneous shape distribution and slight agglomerations (Fig. 7a<sub>1</sub>). However,  $\text{SnFe}_{12}\text{O}_{19}$  reveals a slightly uniform distribution of crystallized NPs (Fig. 7b<sub>1</sub>). On the other hand,  $\text{SrFe}_{12}\text{O}_{19}$  shows the formation of nano-sized grains and uniform particle shape distribution (Fig. 7c<sub>1</sub>). Moreover, all EDX elemental mapping images indicate that the main constituent elements of the synthesized  $\text{MFe}_{12}\text{O}_{19}$  nanostructures are well-dispersed throughout the structure (Fig. 7a<sub>2</sub>–c<sub>2</sub>).

TEM analysis was performed to further investigate the shape and size of the as-synthesized  $\text{MFe}_{12}\text{O}_{19}$  nanostructures (Fig. 8). The TEM images of  $\text{CuFe}_{12}\text{O}_{19}$  reveal spherical nanoparticles with a size range of approximately 75–85 nm, and confirm the presence of tightly agglomerated NPs (Fig. 8a). The TEM images of  $\text{SnFe}_{12}\text{O}_{19}$  reveal small platelets forming large spherical grains, with an average size of about 40–80 nm (Fig. 8b), while the TEM images of  $\text{SrFe}_{12}\text{O}_{19}$  reveal interconnected spherical NPs with a size range of about 25–55 nm (Fig. 8c).

Fig. 9 shows the nitrogen adsorption–desorption isotherms of  $\text{CuFe}_{12}\text{O}_{19}$ ,  $\text{SnFe}_{12}\text{O}_{19}$  and  $\text{SrFe}_{12}\text{O}_{19}$  NPs. According to the IUPAC classification, the isotherms of the  $\text{MFe}_{12}\text{O}_{19}$  NPs may be assigned to type III, III and II for the  $\text{CuFe}_{12}\text{O}_{19}$ ,  $\text{SnFe}_{12}\text{O}_{19}$  and  $\text{SrFe}_{12}\text{O}_{19}$  NPs, respectively. The pore size distributions (BJH model) of all  $\text{MFe}_{12}\text{O}_{19}$  NPs are presented in the inset spectra in Fig. 9a–c. The BJH average pore diameters of  $\text{CuFe}_{12}\text{O}_{19}$ ,  $\text{SnFe}_{12}\text{O}_{19}$  and  $\text{SrFe}_{12}\text{O}_{19}$  NPs are found to be 12.98, 14.95 and 4.89 nm, respectively. According to the IUPAC, these average values indicate that the as-synthesized  $\text{MFe}_{12}\text{O}_{19}$  are classified as a mesoporous nanomaterial.<sup>57,58</sup> Moreover, the BET surface area of the obtained NPs was found to be 1.87, 5.25 and 24.91  $\text{m}^2 \text{g}^{-1}$ , respectively.

To evaluate the stability of the as-prepared  $\text{MFe}_{12}\text{O}_{19}$  for potential catalytic applications, zeta potential (ZP) measurements were carried out on  $\text{MFe}_{12}\text{O}_{19}$  NPs dispersed in a solvent (acetonitrile; acetone or deionized water). The  $\text{CuFe}_{12}\text{O}_{19}$ ,  $\text{SnFe}_{12}\text{O}_{19}$  and  $\text{SrFe}_{12}\text{O}_{19}$  NPs present ZP values of  $-24.8$ ,  $-16.9$

Table 2 Hyperfine parameters of the room temperature Mössbauer spectra of  $\text{CuFe}_{12}\text{O}_{19}$ ,  $\text{SrFe}_{12}\text{O}_{19}$  and  $\text{SnFe}_{12}\text{O}_{19}$

| $\text{MFe}_{12}\text{O}_{19}$                                                      | Component | Area (%) | IS ( $\text{mm s}^{-1}$ ) | $B_{\text{hf}}$ (T) | QS ( $\text{mm s}^{-1}$ ) | Site        |
|-------------------------------------------------------------------------------------|-----------|----------|---------------------------|---------------------|---------------------------|-------------|
| $\text{CuFe}_{12}\text{O}_{19} = \{\text{CuFe}_2\text{O}_4\text{-Fe}_2\text{O}_3\}$ | Sextet-1  | 72.35    | 0.36                      | 51.71               | —                         | Octahedral  |
|                                                                                     | Sextet-2  | 12.15    | 0.36                      | 50.16               | —                         | Tetrahedral |
|                                                                                     | Doublet   | 15.50    | 0.59                      | —                   | 2.65                      | —           |
| $\text{SrFe}_{12}\text{O}_{19}$                                                     | Sextet-1  | 25.12    | 0.28                      | 51.95               | —                         | 4f2         |
|                                                                                     | Sextet-2  | 7.00     | 0.39                      | 50.93               | —                         | 2a          |
|                                                                                     | Sextet-3  | 10.96    | 0.26                      | 49.13               | —                         | 4f1         |
|                                                                                     | Sextet-4  | 55.94    | 0.36                      | 40.90               | —                         | 12k         |
|                                                                                     | Sextet-5  | 0.98     | 0.38                      | 34.95               | —                         | 2b          |
| $\text{SnFe}_{12}\text{O}_{19} = \{\text{SnO}_2\text{-Fe}_2\text{O}_3\}$            | Doublet   | 100      | 0.41                      | —                   | 0.20                      | —           |

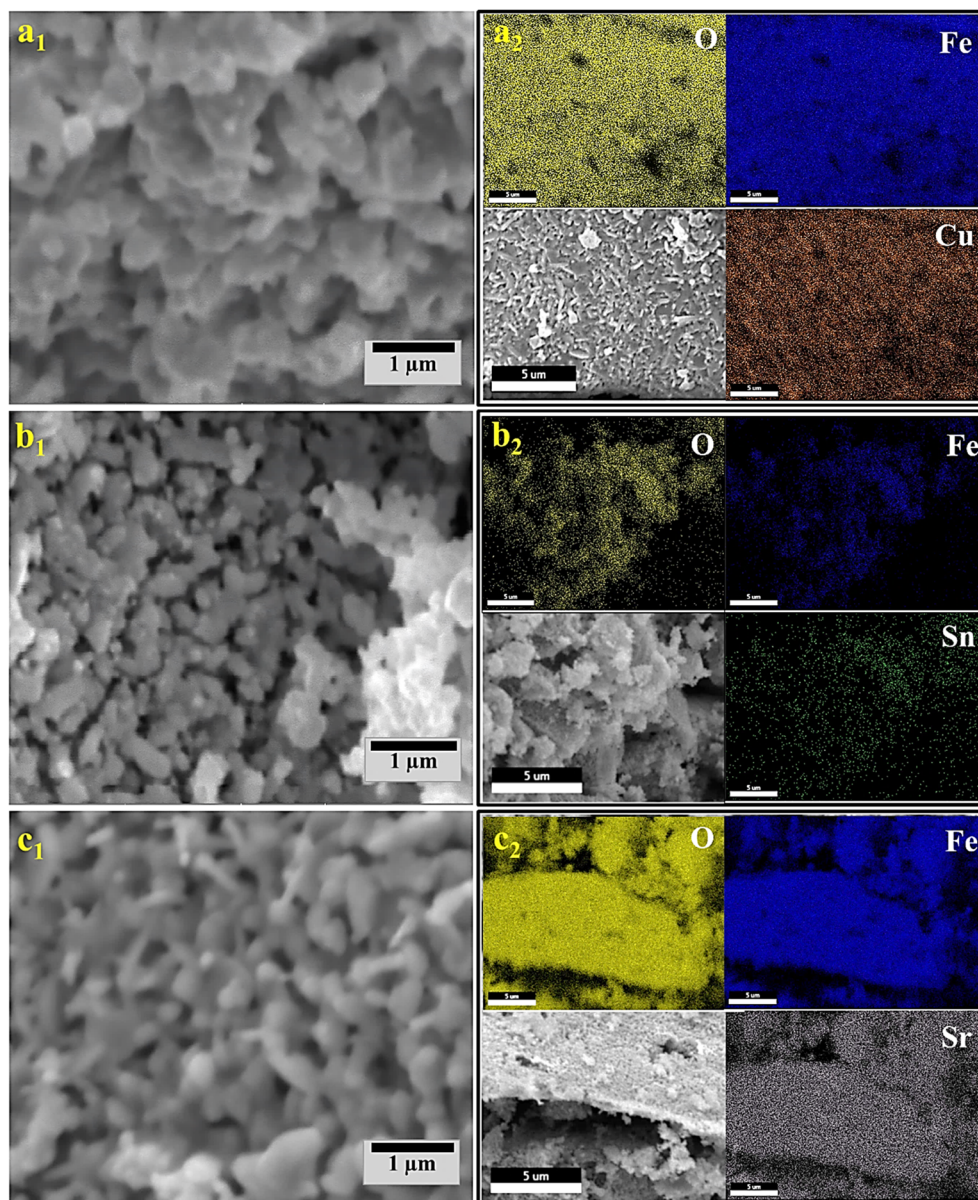


Fig. 7 SEM images and EDX elemental maps of (a)  $\text{CuFe}_{12}\text{O}_{19}$ , (b)  $\text{SnFe}_{12}\text{O}_{19}$  and (c)  $\text{SrFe}_{12}\text{O}_{19}$ .

and  $-20.6$  mV, respectively. Accordingly, it was reported that NPs manifesting  $-25 > \text{ZP} > +25$  mV usually indicate a high degree of stability.<sup>59</sup> Indeed, the obtained surface charge values indicate that the prepared NPs exhibit stabilities ranging from good to a high degree of stability. In addition, the obtained ZP values of the synthesized  $\text{MFe}_{12}\text{O}_{19}$  confirm the observed fluctuation in particle agglomeration ( $\text{Cu} > \text{Sr} > \text{Sn}$ ) during the microscopic study ( $\text{CuFe}_{12}\text{O}_{19}$  presents a threshold ZP value).

### 3.2. Catalytic studies

The catalytic activity of the as-synthesized  $\text{MFe}_{12}\text{O}_{19}$  NPs were evaluated in the selective oxidation reaction of aromatic olefins. Hence, styrene was chosen as a model substrate to conduct the

optimization study of the catalytic oxidation. Moreover, preliminary catalytic tests of  $\text{MFe}_{12}\text{O}_{19}$  were focused on the selective formation of styrene oxide or benzaldehyde, while  $t\text{BHP}$  or  $\text{H}_2\text{O}_2$  were used as the oxidizing agent (Scheme 1 and Table 3).

In the absence of a catalyst, the oxidation reaction gives only a conversion of up to 8% (Table 3). However, the  $\text{CuFe}_{12}\text{O}_{19}$  nanoparticles exhibited the highest efficiency and selectivity in the presence of both oxidizing agents ( $t\text{BHP}$  or  $\text{H}_2\text{O}_2$ ). While the use of  $\text{H}_2\text{O}_2$  in acetone provides a high selectivity towards benzaldehyde (80%) in the presence of  $\text{CuFe}_{12}\text{O}_{19}$ , switching to  $t\text{BHP}$  in acetonitrile resulted in two times higher selectivity towards styrene oxide formation (61%) compared to benzaldehyde (30%). Therefore, both reaction conditions (1 and 2) were optimized for a better catalytic selectivity throughout the study



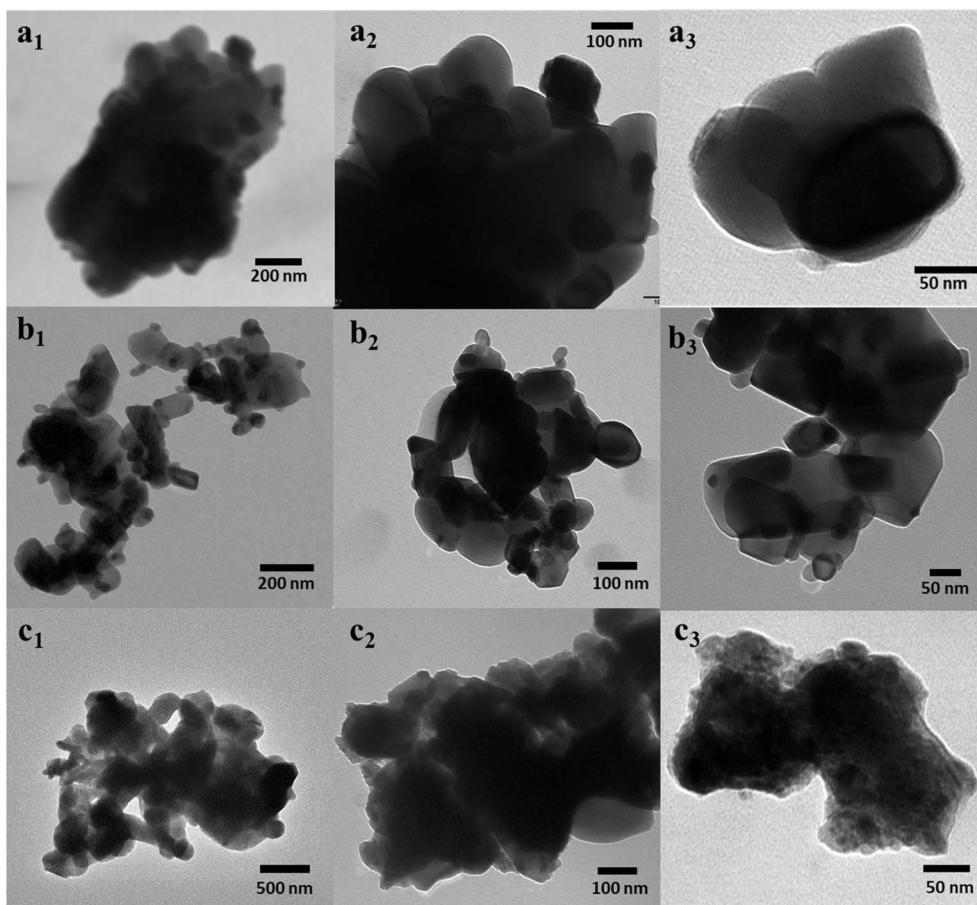


Fig. 8 TEM images of (a)  $\text{CuFe}_{12}\text{O}_{19}$ , (b)  $\text{SnFe}_{12}\text{O}_{19}$  and (c)  $\text{SrFe}_{12}\text{O}_{19}$ .

of various parameters: the catalyst amount, reaction time, temperature, amount of oxidizing agent and solvent nature (Scheme 2).

To investigate the active site responsible for the obtained catalytic performance, we studied the catalytic activity of both  $\text{CuFe}_2\text{O}_4$  and  $\text{Fe}_2\text{O}_3$  compared to the as-prepared composite structure  $\text{CuFe}_{12}\text{O}_{19}$  (Table 4). Indeed, the XRD pattern and Rietveld refinement of  $\text{CuFe}_{12}\text{O}_{19}$  illustrate the presence of both  $\text{CuFe}_2\text{O}_4$  and  $\text{Fe}_2\text{O}_3$  phases as the composite nanostructure ( $\text{CuFe}_{12}\text{O}_{19} = \{\text{CuFe}_2\text{O}_4\text{-Fe}_2\text{O}_3\}$  composite). Hence, the catalytic oxidation in the presence of  $\text{CuFe}_{12}\text{O}_{19}$  reveals high conversion and good selectivity compared to  $\text{CuFe}_2\text{O}_4$  or  $\text{Fe}_2\text{O}_3$  for both reaction conditions. Consequently, the composite structure of the as-prepared  $\text{CuFe}_{12}\text{O}_{19}$  NPs effectively enhances the catalytic activity and reusability of the developed nanocatalyst, owing to the synergistic catalytic effect in a single magnetically recoverable nanostructure.

### 3.3. Optimization of the $\text{CuFe}_{12}\text{O}_{19}$ catalyzed oxidation of styrene

**3.3.1. Effect of solvent.** An examination of the protic and aprotic solvents on the model reaction using  $\text{CuFe}_{12}\text{O}_{19}$  as the catalyst and *t*BHP or  $\text{H}_2\text{O}_2$  as the oxidizing agent has been

carried out (Table 5). On the one hand, the presence of *t*BHP in polar and aprotic solvents (acetonitrile, acetone and THF) promotes the selective formation of styrene oxide, compared to the protic ones. On the other hand, acetone provides the best selectivity towards benzaldehyde when using  $\text{H}_2\text{O}_2$  as the oxidizing agent. For further optimizations, the catalytic oxidation will be carried out in the presence of *t*BHP in acetonitrile for the selective formation of epoxide (condition 1), while  $\text{H}_2\text{O}_2$  in acetone will be used for the selective synthesis of aldehyde (condition 2).

**3.3.2. Effect of the reaction temperature.** Table 6 shows the effect of temperature on the selective catalytic oxidation of styrene in the presence of  $\text{CuFe}_{12}\text{O}_{19}$  nanoparticles as the catalyst. In the presence of *t*BHP, the optimum conversion/selectivity was obtained at 60 °C and the elevated temperature (80 °C) resulted in a decrease of the styrene oxide selectivity due to the epoxide ring-opening. Moreover, when the reaction was conducted in the presence of  $\text{H}_2\text{O}_2$  as the oxidizing agent, the increase of temperature to 80 °C resulted in a total styrene conversion and a high selectivity towards benzaldehyde. Therefore, further optimization studies were conducted at 60 °C and 80 °C for conditions 1 and 2, respectively.

**3.3.3. Effect of the catalyst amount.** The selective catalytic oxidation of styrene was carried out in the presence of different




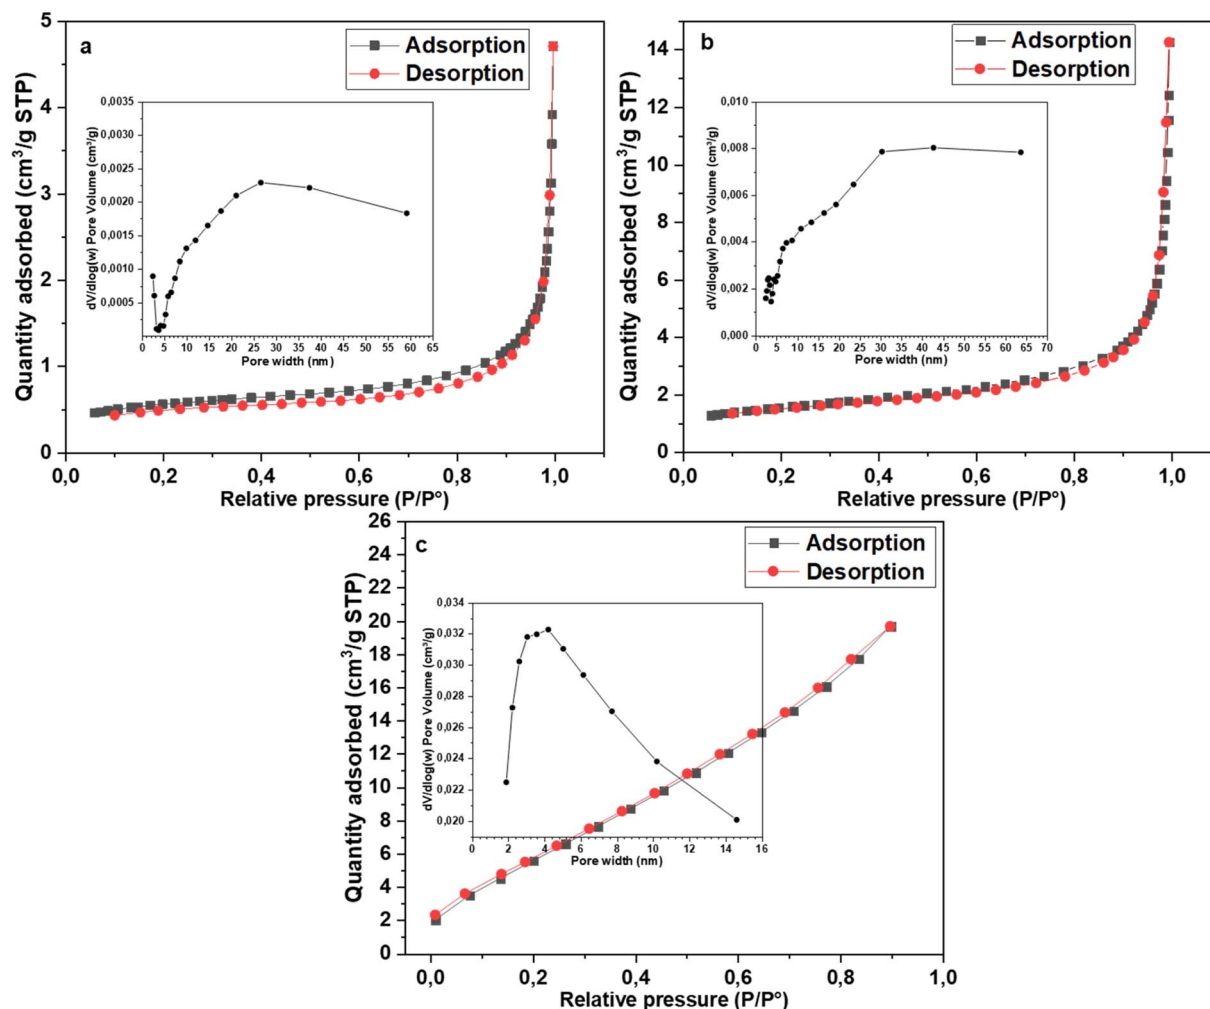


Fig. 9  $\text{N}_2$  adsorption-desorption isotherm and BJH pore diameter distribution of (a)  $\text{CuFe}_{12}\text{O}_{19}$ , (b)  $\text{SnFe}_{12}\text{O}_{19}$  and (c)  $\text{SrFe}_{12}\text{O}_{19}$ .

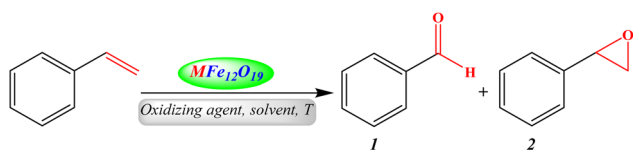


Scheme 1 Selective catalytic oxidation of styrene.

amounts of  $\text{CuFe}_{12}\text{O}_{19}$  as the catalyst (Table 7). When the reaction was performed with *t*BHP as the oxidant, the best result was obtained with 20 mg of  $\text{CuFe}_{12}\text{O}_{19}$ , giving a selective formation of styrene oxide of 61%. Similarly, in the presence of  $\text{H}_2\text{O}_2$ , the optimal  $\text{CuFe}_{12}\text{O}_{19}$  amount was 20 mg with a total conversion and a high selectivity of benzaldehyde of up to 81%.

Table 3 Catalytic oxidation<sup>a</sup> of styrene in the presence of *t*-BHP<sup>b</sup> or  $\text{H}_2\text{O}_2$ <sup>c</sup>

| Reaction    | Catalyst                        | <i>T</i> (°C) | Ox. agent              | Solvent      | Conversion <sup>d</sup> (%) | Yield <sup>d</sup> (%) |               |
|-------------|---------------------------------|---------------|------------------------|--------------|-----------------------------|------------------------|---------------|
|             |                                 |               |                        |              |                             | Benzaldehyde           | Styrene oxide |
| Condition 1 | —                               | 60            | <i>t</i> BHP           | Acetonitrile | 8                           | 7                      | —             |
|             | $\text{CuFe}_{12}\text{O}_{19}$ | 60            | <i>t</i> BHP           | Acetonitrile | 93                          | 30                     | 61            |
|             | $\text{SnFe}_{12}\text{O}_{19}$ | 60            | <i>t</i> BHP           | Acetonitrile | 20                          | 11                     | 8             |
|             | $\text{SrFe}_{12}\text{O}_{19}$ | 60            | <i>t</i> BHP           | Acetonitrile | 30                          | 11                     | 18            |
| Condition 2 | —                               | 80            | $\text{H}_2\text{O}_2$ | Acetone      | 4                           | 4                      | —             |
|             | $\text{CuFe}_{12}\text{O}_{19}$ | 80            | $\text{H}_2\text{O}_2$ | Acetone      | 100                         | 80                     | —             |
|             | $\text{SnFe}_{12}\text{O}_{19}$ | 80            | $\text{H}_2\text{O}_2$ | Acetone      | 100                         | 28                     | —             |
|             | $\text{SrFe}_{12}\text{O}_{19}$ | 80            | $\text{H}_2\text{O}_2$ | Acetone      | 72                          | 40                     | —             |

<sup>a</sup> General reaction conditions: 1.92 mmol of styrene with 3 eq. of oxidizing agent and 2 ml of solvent for 24 h. <sup>b</sup> Condition 1: *t*BHP in acetonitrile at 60 °C. <sup>c</sup> Condition 2:  $\text{H}_2\text{O}_2$  in acetone at 80 °C. <sup>d</sup> The conversion and yields were determined by GC using dodecane as the internal standard.

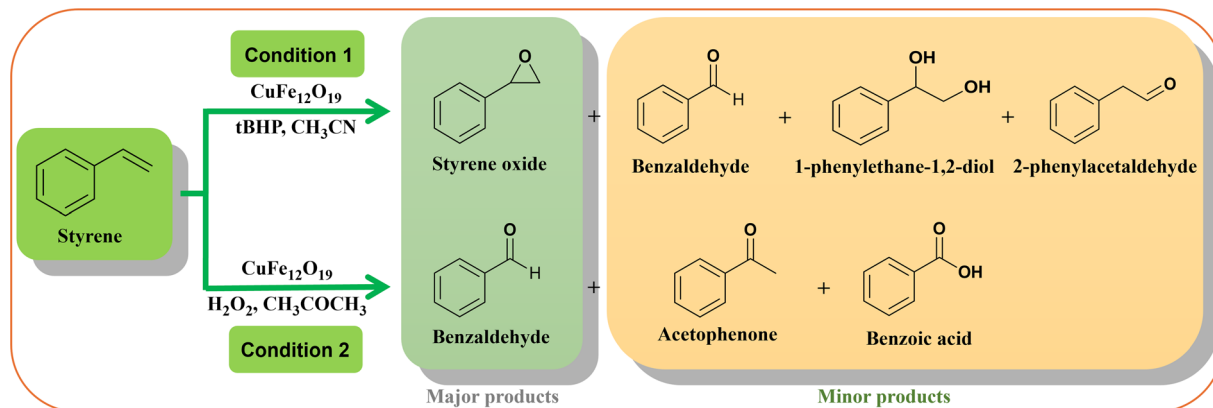Scheme 2 Catalytic oxidation of styrene in the presence of  $t\text{BHP}$  or  $\text{H}_2\text{O}_2$ .Table 4 Comparison of the catalytic activity of the as-prepared nanomaterials in catalytic styrene oxidation<sup>a</sup>

| Oxidizing agent        | Catalyst                                          | Conversion <sup>b</sup> (%) | Yield <sup>b</sup> (%) |               |
|------------------------|---------------------------------------------------|-----------------------------|------------------------|---------------|
|                        |                                                   |                             | Benzaldehyde           | Styrene oxide |
| $t\text{BHP}$          | $\text{Fe}_2\text{O}_3$                           | 86                          | 34                     | 39            |
|                        | $\text{CuFe}_2\text{O}_4$                         | 99                          | 14                     | 37            |
|                        | <b><math>\text{CuFe}_{12}\text{O}_{19}</math></b> | <b>93</b>                   | <b>30</b>              | <b>61</b>     |
| $\text{H}_2\text{O}_2$ | $\text{Fe}_2\text{O}_3$                           | 18                          | 11                     | Trace         |
|                        | $\text{CuFe}_2\text{O}_4$                         | 5                           | Trace                  | —             |
|                        | <b><math>\text{CuFe}_{12}\text{O}_{19}</math></b> | <b>100</b>                  | <b>81</b>              | —             |

<sup>a</sup> General reaction conditions: 1.92 mmol of styrene, 3 eq. of oxidizing agent ( $t\text{BHP}$ , acetonitrile at 60 °C or  $\text{H}_2\text{O}_2$ , acetone at 80 °C), catalyst (20 mg) and 2 ml of solvent for 24 h. <sup>b</sup> The conversion and yields were determined by GC using dodecane as the internal standard.

Table 5 Effect of solvent on the styrene oxidation in the presence of  $\text{CuFe}_{12}\text{O}_{19}$  NPs as the catalyst<sup>a</sup>

| Oxidizing agent        | Solvent              | Conversion <sup>b</sup> (%) | Yield <sup>b</sup> (%) |               |
|------------------------|----------------------|-----------------------------|------------------------|---------------|
|                        |                      |                             | Benzaldehyde           | Styrene oxide |
| $t\text{BHP}$          | None                 | 24                          | 6                      | 17            |
|                        | $\text{H}_2\text{O}$ | 17                          | 16                     | —             |
|                        | Methanol             | 45                          | 26                     | 13            |
|                        | Ethanol              | 18                          | 14                     | 3             |
|                        | <b>Acetonitrile</b>  | <b>93</b>                   | <b>30</b>              | <b>61</b>     |
|                        | THF                  | 65                          | 19                     | 43            |
|                        | Acetone              | 63                          | 17                     | 39            |
| $\text{H}_2\text{O}_2$ | None                 | 5                           | 5                      | —             |
|                        | $\text{H}_2\text{O}$ | 4                           | 4                      | —             |
|                        | Methanol             | 82                          | 10                     | —             |
|                        | Ethanol              | 100                         | 17                     | —             |
|                        | Acetonitrile         | 22                          | 20                     | —             |
|                        | THF                  | 79                          | 45                     | —             |
|                        | <b>Acetone</b>       | <b>100</b>                  | <b>81</b>              | —             |

<sup>a</sup> General reaction conditions: 1.92 mmol of styrene, 3 eq. of oxidizing agent ( $t\text{BHP}$  at 60 °C or  $\text{H}_2\text{O}_2$  at 80 °C),  $\text{CuFe}_{12}\text{O}_{19}$  (20 mg) and 2 ml of solvent for 24 h. <sup>b</sup> The conversion and yields were determined by GC using dodecane as the internal standard.

Therefore, further optimization studies were conducted using 20 mg of catalyst.

**3.3.4. Effect of oxidizing agent/styrene molar ratio.** The selective catalytic oxidation of styrene was performed by varying the molar ratio of the oxidizing agent/styrene (Table 8). The

increase of the  $t\text{BHP}$ /styrene molar ratio to 3 enhances both conversion and selectivity of styrene oxide. However, with a  $t\text{BHP}$ /styrene molar ratio of 4, the selectivity of styrene oxide decreases due to the formation of benzoic acid. Similarly, a  $\text{H}_2\text{O}_2$ /styrene molar ratio of 3 gave the best result.



**Table 6** Effect of the reaction temperature on the styrene oxidation in the presence of CuFe<sub>12</sub>O<sub>19</sub> NPs as the catalyst<sup>a</sup>

| Reaction                 | Temperature (°C) | Conversion <sup>d</sup> (%) | Yield <sup>d</sup> (%) |               |
|--------------------------|------------------|-----------------------------|------------------------|---------------|
|                          |                  |                             | Benzaldehyde           | Styrene oxide |
| Condition 1 <sup>b</sup> | 50               | 64                          | 20                     | 40            |
|                          | <b>60</b>        | <b>93</b>                   | <b>30</b>              | <b>61</b>     |
|                          | 70               | 100                         | 32                     | 59            |
|                          | 80               | 100                         | 44                     | 11            |
| Condition 2 <sup>c</sup> | 50               | 23                          | 21                     | —             |
|                          | 60               | 24                          | 22                     | —             |
|                          | 70               | 52                          | 50                     | —             |
|                          | <b>80</b>        | <b>100</b>                  | <b>81</b>              | —             |

<sup>a</sup> General reaction conditions: 1.92 mmol of styrene with 3 eq. of oxidizing agent, CuFe<sub>12</sub>O<sub>19</sub> (20 mg) and 2 ml of solvent for 24 h. <sup>b</sup> Condition 1: *t*BHP in acetonitrile. <sup>c</sup> Condition 2: H<sub>2</sub>O<sub>2</sub> in acetone. <sup>d</sup> The conversion and yields were determined by GC using dodecane as the internal standard.

**Table 7** Effect of the catalyst amount on the styrene oxidation in the presence of CuFe<sub>12</sub>O<sub>19</sub> NPs as the catalysts<sup>a</sup>

| Reaction                 | Catalyst amount (mg) | Conversion <sup>d</sup> (%) | Yield <sup>d</sup> (%) |               |
|--------------------------|----------------------|-----------------------------|------------------------|---------------|
|                          |                      |                             | Benzaldehyde           | Styrene oxide |
| Condition 1 <sup>b</sup> | 10                   | 87                          | 33                     | 51            |
|                          | 15                   | 91                          | 32                     | 57            |
|                          | <b>20</b>            | <b>93</b>                   | <b>30</b>              | <b>61</b>     |
|                          | 25                   | 96                          | 36                     | 56            |
|                          | 30                   | 85                          | 33                     | 51            |
| Condition 2 <sup>c</sup> | 10                   | 85                          | 68                     | —             |
|                          | 15                   | 88                          | 70                     | —             |
|                          | <b>20</b>            | <b>100</b>                  | <b>81</b>              | —             |
|                          | 25                   | 100                         | 67                     | —             |
|                          | 30                   | 100                         | 60                     | —             |

<sup>a</sup> General reaction conditions: 1.92 mmol of styrene with 3 eq. of oxidizing agent, CuFe<sub>12</sub>O<sub>19</sub> and 2 ml of solvent for 24 h. <sup>b</sup> Condition 1: *t*BHP in acetonitrile at 60 °C. <sup>c</sup> Condition 2: H<sub>2</sub>O<sub>2</sub> in acetone at 80 °C. <sup>d</sup> The conversion and yields were determined by GC using dodecane as the internal standard.

**3.3.5. Effect of the reaction time.** A kinetic study of the selective catalytic oxidation of styrene was carried out (Table 9). The evolution of the reaction *versus* time shows that styrene oxide or benzaldehyde were formed as major products in the presence of *t*BHP and H<sub>2</sub>O<sub>2</sub>, respectively. The best result was obtained within 24 h.

**3.3.6. Effect of basicity.** To improve the epoxide selectivity in the oxidation of olefins, the effect of the reaction medium basicity should be taken into consideration. Indeed, the selective catalytic oxidation of styrene-to-styrene oxide was performed using different amounts of urea to assess the effect of basicity (Fig. 10). In the presence of 20 mg of urea (17.34 mol%),

**Table 8** Effect of the oxidizing agent/styrene molar ratio on the styrene oxidation in the presence of CuFe<sub>12</sub>O<sub>19</sub> NPs as catalysts<sup>a</sup>

| Reaction                 | Oxidizing agent/styrene | Conversion <sup>d</sup> (%) | Yield <sup>d</sup> (%) |               |
|--------------------------|-------------------------|-----------------------------|------------------------|---------------|
|                          |                         |                             | Benzaldehyde           | Styrene oxide |
| Condition 1 <sup>b</sup> | 1                       | 43                          | 15                     | 24            |
|                          | 2                       | 66                          | 19                     | 42            |
|                          | <b>3</b>                | <b>93</b>                   | <b>30</b>              | <b>61</b>     |
|                          | 4                       | 80                          | 30                     | 45            |
| Condition 2 <sup>c</sup> | 1                       | 10                          | 9                      | —             |
|                          | 2                       | 40                          | 26                     | —             |
|                          | <b>3</b>                | <b>100</b>                  | <b>81</b>              | —             |
|                          | 4                       | 100                         | 48                     | —             |

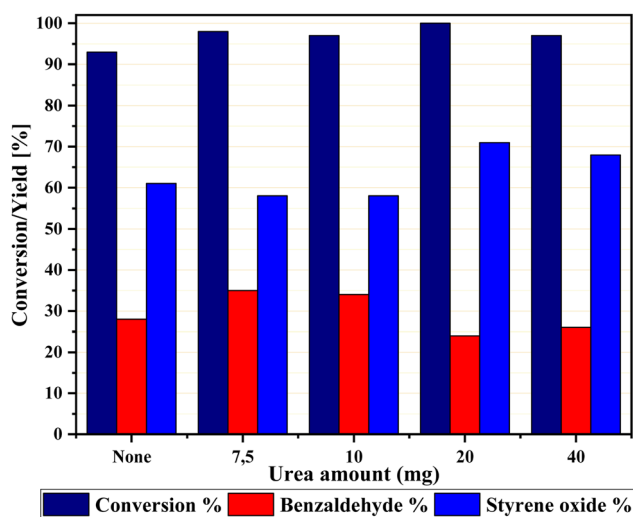
<sup>a</sup> General reaction conditions: 1.92 mmol of styrene, oxidizing agent, CuFe<sub>12</sub>O<sub>19</sub> (20 mg) and 2 ml of solvent for 24 h. <sup>b</sup> Condition 1: *t*BHP in acetonitrile at 60 °C. <sup>c</sup> Condition 2: H<sub>2</sub>O<sub>2</sub> in acetone at 80 °C. <sup>d</sup> The conversion and yields were determined by GC using dodecane as the internal standard.



**Table 9** Effect of the reaction time on the styrene oxidation in the presence of CuFe<sub>12</sub>O<sub>19</sub> NPs as catalysts<sup>a</sup>

| Reaction                 | Time (h) | Conversion <sup>d</sup> (%) | Yield <sup>d</sup> (%) |               |
|--------------------------|----------|-----------------------------|------------------------|---------------|
|                          |          |                             | Benzaldehyde           | Styrene oxide |
| Condition 1 <sup>b</sup> | 3        | 28                          | 12                     | 12            |
|                          | 6        | 48                          | 20                     | 21            |
|                          | 12       | 78                          | 29                     | 46            |
|                          | 15       | 83                          | 30                     | 50            |
|                          | 18       | 87                          | 30                     | 55            |
|                          | 24       | 93                          | 30                     | 61            |
| Condition 2 <sup>c</sup> | 3        | 9                           | 8                      | —             |
|                          | 6        | 40                          | 36                     | —             |
|                          | 12       | 68                          | 61                     | —             |
|                          | 15       | 77                          | 67                     | —             |
|                          | 18       | 83                          | 68                     | —             |
|                          | 24       | 100                         | 81                     | —             |

<sup>a</sup> General reaction conditions: 1.92 mmol of styrene with 3 eq. of oxidizing agent, CuFe<sub>12</sub>O<sub>19</sub> (20 mg) and 2 ml of solvent. <sup>b</sup> Condition 1: *t*BHP in acetonitrile at 60 °C. <sup>c</sup> Condition 2: H<sub>2</sub>O<sub>2</sub> in acetone at 80 °C. <sup>d</sup> The conversion and yields were determined by GC using dodecane as the internal standard.

**Fig. 10** Effect of urea in the presence of *t*BHP and CuFe<sub>12</sub>O<sub>19</sub> as the catalyst.

a total conversion was obtained and the selectivity of styrene oxide increases to 72%. This result can be explained by the stabilization effect of urea on the epoxide function, which avoids the epoxide ring-opening *via* hydrolysis reaction. Indeed, Liu *et al.* have reported that the basicity of the solvent medium increases the styrene oxide selectivity.<sup>17</sup>


### 3.4. Heterogeneity test

A hot-filtration test was performed to investigate the heterogeneity of the CuFe<sub>12</sub>O<sub>19</sub> NPs catalytic system (Fig. 11). After 12 h of the catalytic oxidation of styrene, the catalyst was separated from the reaction mixture by an external magnetic field and the obtained filtrate was continually stirred under the same reaction conditions. The results indicated that no significant enhancement of the styrene conversion was observed even after completing 24 h of reaction time. This result clearly indicates

that the CuFe<sub>12</sub>O<sub>19</sub> nanoparticles act as a heterogeneous catalyst in the styrene oxidation.

### 3.5. Recycling of catalyst

Since catalyst recyclability has great potential for practical applications, the reusability of magnetic CuFe<sub>12</sub>O<sub>19</sub> NPs was evaluated in five consecutive cycles in the selective styrene oxidation reaction under gram-scale conditions (Fig. 12). In the presence of *t*BHP, the catalytic activity of CuFe<sub>12</sub>O<sub>19</sub> NPs slightly decreases in terms of the styrene conversion and styrene oxide selectivity during the consecutive runs. Hence, the investigation of XRD analysis shows that the identity of the recovered CuFe<sub>12</sub>O<sub>19</sub> catalyst remains like the fresh one (Fig. 13a). However, the SEM image shows agglomerated particles with a change in the surface morphology (Fig. 13b), which could explain the noticeable drop in the reaction conversion and selectivity. On the other hand, the

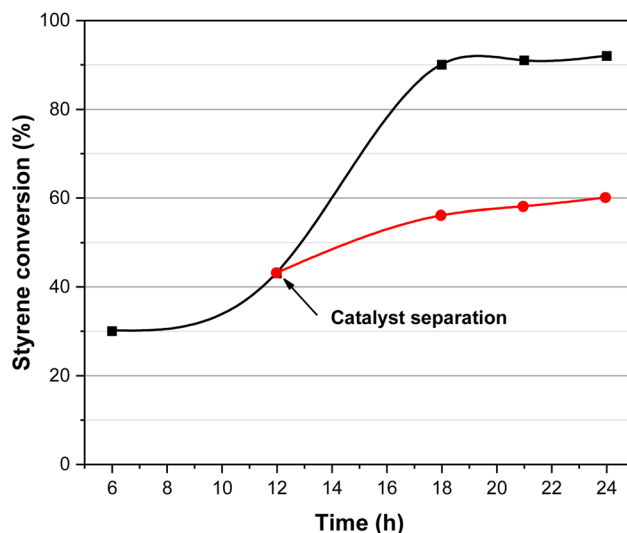**Fig. 11** Heterogeneity test of the CuFe<sub>12</sub>O<sub>19</sub> nanoparticles.

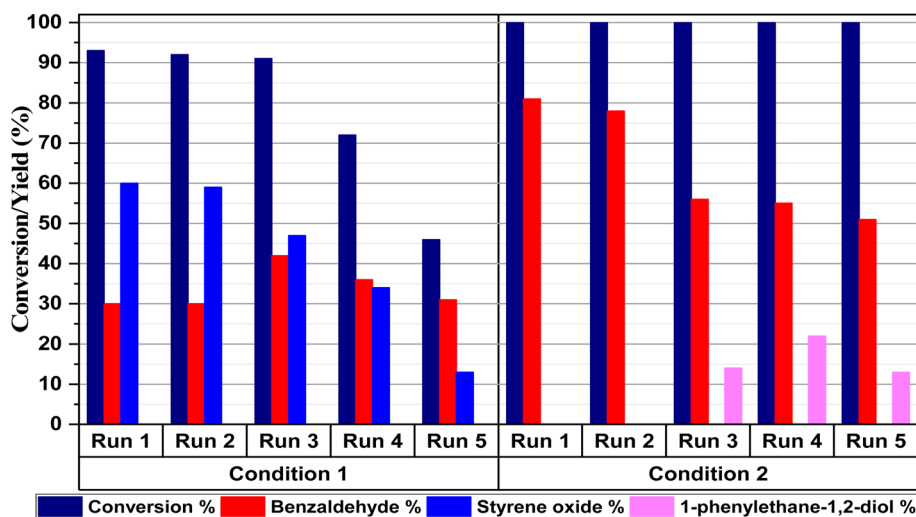


Fig. 12 CuFe<sub>12</sub>O<sub>19</sub> reusability in the gram-scale selective catalytic oxidation of styrene.

selective catalytic reaction carried out in presence of H<sub>2</sub>O<sub>2</sub> and CuFe<sub>12</sub>O<sub>19</sub> exhibits a total and stable conversion within the five runs with a slight decrease in benzaldehyde selectivity over the runs. Furthermore, the XRD patterns and SEM images of the recycled CuFe<sub>12</sub>O<sub>19</sub> catalyst present no obvious changes compared to the fresh one (Fig. 13a and c).

### 3.6. Catalytic oxidation of styrene derivatives

With the optimized reaction conditions (1 and 2) in hand, the scope and limitations of the as-developed catalytic system

MFe<sub>12</sub>O<sub>19</sub> were investigated in the catalytic oxidation of various aromatic olefins in the presence of CuFe<sub>12</sub>O<sub>19</sub> NPs as catalysts (Table 10). All studied olefins were selectively converted to the corresponding oxygenated products in excellent to good yields.

### 3.7. Comparison of the catalytic performance of MNPs

To shed more light on the scope of CuFe<sub>12</sub>O<sub>19</sub> NPs in organic synthesis as MNPs catalysts, the catalytic performance of other MNPs-based catalysts that have been tested in styrene catalytic oxidation so far is summarized in Table 11. Compared to the

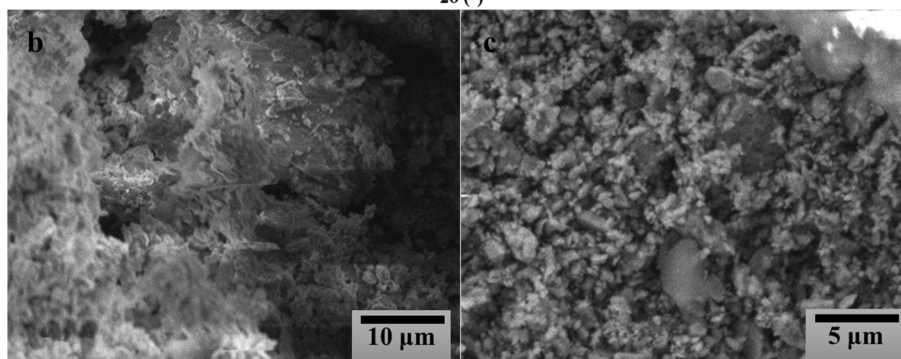
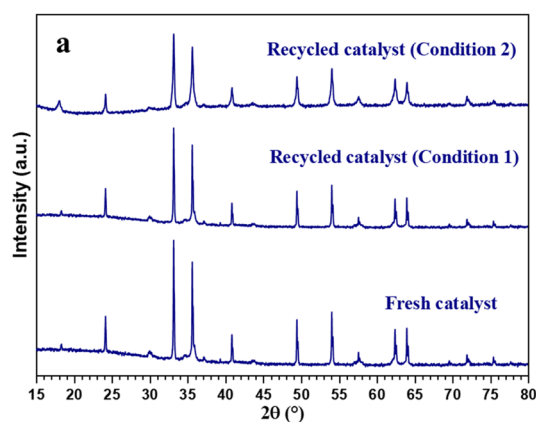































Fig. 13 XRD patterns of the fresh and recycled CuFe<sub>12</sub>O<sub>19</sub> (a), and SEM images of CuFe<sub>12</sub>O<sub>19</sub> after five runs while using (b) tBHP or (c) H<sub>2</sub>O<sub>2</sub>.



Table 10 Catalytic oxidation of styrene derivatives in presence of CuFe<sub>12</sub>O<sub>19</sub> NPs as catalyst<sup>a</sup>

| Reaction                 | Substrate                                                                           | Conversion <sup>d</sup> (%) | Yield <sup>d</sup> (%)                                                                    |                                                                                                |                                                                                              |
|--------------------------|-------------------------------------------------------------------------------------|-----------------------------|-------------------------------------------------------------------------------------------|------------------------------------------------------------------------------------------------|----------------------------------------------------------------------------------------------|
| Condition 1 <sup>b</sup> |    | 100                         |          | <br>24      | <br>Trace |
|                          |    | 98                          |          | <br>35      | <br>7     |
|                          |    | 100                         |          | —                                                                                              | —                                                                                            |
|                          |    | 100                         |          | <br>14      | <br>16    |
|                          |   | 80                          |         | —                                                                                              | —                                                                                            |
|                          |  | 100                         | <br>81 | <br>10    | <br>7   |
| Condition 2 <sup>c</sup> |  | 71                          | <br>60 | <br>9     | —                                                                                            |
|                          |  | 80                          | <br>25 | <br>39    | —                                                                                            |
|                          |  | 58                          | <br>45 | <br>Trace | —                                                                                            |

<sup>a</sup> General reaction conditions: 1.92 mmol of styrene with 3 eq. of oxidizing agent, CuFe<sub>12</sub>O<sub>19</sub> (20 mg) and 2 ml of solvent for 24 h. <sup>b</sup> Condition 1: *t*BHP in acetonitrile with 20 mg of urea at 60 °C. <sup>c</sup> Condition 2: H<sub>2</sub>O<sub>2</sub> in acetone at 80 °C. <sup>d</sup> The conversion and yields were determined by GC using dodecane as the internal standard.



Table 11 Comparison of the catalytic activity of MNPs towards the selective oxidation of styrene

| Catalyst                                         | Ox. agent                                                                                                | Conv. (%) | Select. SO (%) | Select. BA (%) | Reusability (conv. % : run) | Ref.         |
|--------------------------------------------------|----------------------------------------------------------------------------------------------------------|-----------|----------------|----------------|-----------------------------|--------------|
| CoFe <sub>2</sub> O <sub>4</sub>                 | <i>t</i> BHP                                                                                             | 81        | 76             | 23             | 92 : 5                      | 17           |
| $\alpha$ -Fe <sub>2</sub> O <sub>3</sub>         | <i>t</i> BHP                                                                                             | 73        | 77             | ND             | —                           | 60           |
| Au/L-Fe <sub>3</sub> O <sub>4</sub>              | <i>t</i> BHP                                                                                             | 76.1      | 70.1           | 27.5           | —                           | 61           |
| Ag/KOH- $\gamma$ -Fe <sub>2</sub> O <sub>3</sub> | <i>t</i> BHP                                                                                             | 89.6      | 89.7           | 10.3           | 89 : 5                      | 62           |
| MFe <sub>12</sub> O <sub>19</sub>                | CuFe <sub>12</sub> O <sub>19</sub> = {CuFe <sub>2</sub> O <sub>4</sub> -Fe <sub>2</sub> O <sub>3</sub> } | 100       | 72             | 24             | 45 : 5                      | Present work |
|                                                  | SnFe <sub>12</sub> O <sub>19</sub> = {SnO <sub>2</sub> -Fe <sub>2</sub> O <sub>3</sub> }                 | 65        | 26             | 5              | —                           |              |
|                                                  | SrFe <sub>12</sub> O <sub>19</sub>                                                                       | 30        | 11             | 18             | —                           |              |
| SrFe <sub>2</sub> O <sub>4</sub>                 | H <sub>2</sub> O <sub>2</sub>                                                                            | 63.7      | ND             | 32             | 42 : 2                      | 20           |
| BaFe <sub>2</sub> O <sub>4</sub>                 | H <sub>2</sub> O <sub>2</sub>                                                                            | 45.1      | 9.5            | 88.5           | 31 : 3                      | 63           |
| CaFe <sub>2</sub> O <sub>4</sub>                 | H <sub>2</sub> O <sub>2</sub>                                                                            | 37.9      | ND             | 91.1           | —                           | 64           |
| NiFe <sub>2</sub> O <sub>4</sub>                 | H <sub>2</sub> O <sub>2</sub>                                                                            | 31.4      | ND             | 55.6           | —                           | 18           |
| MFe <sub>12</sub> O <sub>19</sub>                | CuFe <sub>12</sub> O <sub>19</sub> = {CuFe <sub>2</sub> O <sub>4</sub> -Fe <sub>2</sub> O <sub>3</sub> } | 100       | —              | 82             | 100 : 5                     | Present work |
|                                                  | SnFe <sub>12</sub> O <sub>19</sub> = {SnO <sub>2</sub> -Fe <sub>2</sub> O <sub>3</sub> }                 | 100       | —              | 28             | —                           |              |
|                                                  | SrFe <sub>12</sub> O <sub>19</sub>                                                                       | 72        | —              | 40             | —                           |              |

previous studies, CuFe<sub>12</sub>O<sub>19</sub> exhibits a high catalytic conversion with good selectivity under both conditions (1 and 2). The higher efficiency of CuFe<sub>12</sub>O<sub>19</sub> MNPs can be attributed to the superior catalytic role of Cu and its synergistic effect with Fe, in comparison to Sn and Sr in the studied MFe<sub>12</sub>O<sub>19</sub> NPs. This can be explained by the synergy between CuFe<sub>2</sub>O<sub>4</sub> and Fe<sub>2</sub>O<sub>3</sub> during the oxidation process, where both Cu and Fe are involved in the coordination with the activated oxidizing agent (*t*BHP or H<sub>2</sub>O<sub>2</sub>). This could lead to the formation of peroxo or superoxo species, such as Fe(III)OO<sup>•</sup> and Cu(II)OO<sup>•</sup>, complexes that may not be formed with Sn and Sr. Additionally, the possible synergistic intersection between Cu<sup>+</sup>/Cu<sup>2+</sup> and Fe<sup>2+</sup>/Fe<sup>3+</sup> redox pairs at the catalyst surface could also contribute to the observed catalytic performance.

## 4. Conclusion

Magnetically separable MFe<sub>12</sub>O<sub>19</sub> NPs were successfully synthesized using the coprecipitation method. As-prepared MFe<sub>12</sub>O<sub>19</sub> (M = Cu, Sn and Sr) NPs exhibited nanoscale particle size, magnetic behavior, mesoporous structure and good recyclability. Advanced characterization studies revealed that SnFe<sub>12</sub>O<sub>19</sub> and CuFe<sub>12</sub>O<sub>19</sub> are not isostructural with the SrFe<sub>12</sub>O<sub>19</sub> M-type hexaferrite, due to confirmed coexistence of SnO<sub>2</sub>-Fe<sub>2</sub>O<sub>3</sub> and CuFe<sub>2</sub>O<sub>4</sub>-Fe<sub>2</sub>O<sub>3</sub> as a composite structure, respectively. The magnetic MFe<sub>12</sub>O<sub>19</sub> nanocatalysts were found to be highly efficient for the selective oxidation reaction of various styrene derivatives compared to other reported MNPs heterogeneous catalysts. Among the as-synthesized MFe<sub>12</sub>O<sub>19</sub> NPs, CuFe<sub>12</sub>O<sub>19</sub> was found to be the best catalyst either in the presence of *t*BHP or H<sub>2</sub>O<sub>2</sub> as the oxidizing agent. The high catalytic activity and good selectivity of CuFe<sub>12</sub>O<sub>19</sub> MNPs could be associated with the synergistic catalytic effect of CuFe<sub>2</sub>O<sub>4</sub> and Fe<sub>2</sub>O<sub>3</sub> in a single magnetically recoverable nanostructure, compared to SnFe<sub>12</sub>O<sub>19</sub> and SrFe<sub>12</sub>O<sub>19</sub>. We can assume that the developed MFe<sub>12</sub>O<sub>19</sub> MNPs present a facile and greener approach using magnetically recyclable nanostructures for the selective catalytic oxidation reaction of olefins.

## Data availability

The device types used for recording spectra and other analytical data that support the findings of this study are included in the manuscript.

## Conflicts of interest

The authors declare that they have no conflicts of interest.

## References

- 1 N. Ma, Y. Yue, W. Hua and Z. Gao, *Appl. Catal., A*, 2003, **251**, 39–47.
- 2 J. Liu, F. Wang, Z. Gu and X. Xu, *Chem. Eng. J.*, 2009, **151**, 319–323.
- 3 S. Tian, C. Peng, J. Dong, Q. Xu, Z. Chen, D. Zhai, Y. Wang, L. Gu, P. Hu, H. Duan, D. Wang and Y. Li, *ACS Catal.*, 2021, **11**, 4946–4954.
- 4 A. Aberkouks, A. A. Mekkaoui, B. Boualy, S. El Houssame, M. Ait Ali and L. El Firdoussi, *Adv. Mater. Sci. Eng.*, 2018, **2018**, 2716435.
- 5 G. Grigoropoulou, J. H. Clark and J. A. Elings, *Green Chem.*, 2003, **5**, 1–7.
- 6 A. Patel and S. Pathan, *Ind. Eng. Chem. Res.*, 2012, **51**, 732–740.
- 7 C. M. Granadeiro, A. D. S. Barbosa, S. Ribeiro, I. C. M. S. Santos, B. De Castro, L. Cunha-Silva and S. S. Balula, *Catal. Sci. Technol.*, 2014, **4**, 1416–1425.
- 8 T. A. G. Duarte, I. C. M. S. Santos, M. M. Q. Simões, M. G. P. M. S. Neves, A. M. V. Cavaleiro and J. A. S. Cavaleiro, *Catal. Lett.*, 2014, **144**, 104–111.
- 9 S. S. Balula, L. Cunha-Silva, I. C. M. S. Santos, A. C. Estrada, A. C. Fernandes, J. A. S. Cavaleiro, J. Pires, C. Freire and A. M. V. Cavaleiro, *New J. Chem.*, 2013, **37**, 2341–2350.
- 10 A. Aberkouks, A. A. Mekkaoui, B. Boualy, S. E. L. Houssame, M. Ait Ali and L. El Firdoussi, *Mater. Today: Proc.*, 2019, **13**, 453–457.



- 11 V. R. Choudhary, R. Jha and P. Jana, *Catal. Commun.*, 2008, **10**, 205–207.
- 12 I. W. Davies, L. Matty, D. L. Hughes and P. J. Reider, *J. Am. Chem. Soc.*, 2001, **123**, 10139–10140.
- 13 M. Nemanashi and R. Meijboom, *Catal. Lett.*, 2013, **143**, 324–332.
- 14 D. Yin, L. Qin, J. Liu, C. Li and Y. Jin, *J. Mol. Catal. A:Chem.*, 2005, **240**, 40–48.
- 15 A. Aberkhouks, A. A. Mekkaoui, M. Ait Ali, L. El Firdoussi and S. El Houssame, *J. Chem.*, 2020, **2020**, 1241952.
- 16 I. T. Horváth and P. T. Anastas, *Chem. Rev.*, 2007, **107**, 2167–2168.
- 17 J. Liu, R. Meng, J. Li, P. Jian, L. Wang and R. Jian, *Appl. Catal., B*, 2019, **254**, 214–222.
- 18 D. Guin, B. Baruwati and S. V. Manorama, *J. Mol. Catal. A:Chem.*, 2005, **242**, 26–31.
- 19 R. Ramanathan and S. Sugunan, *Catal. Commun.*, 2007, **8**, 1521–1526.
- 20 S. K. Pardeshi and R. Y. Pawar, *J. Mol. Catal. A:Chem.*, 2011, **334**, 35–43.
- 21 Ü. Özgür, Y. Alivov and H. Morkoç, *J. Mater. Sci.: Mater. Electron.*, 2009, **20**, 789–834.
- 22 J. M. D. Coey, *J. Alloys Compd.*, 2001, **326**, 2–6.
- 23 P. E. Kazin, L. A. Trusov, D. D. Zaitsev, Y. D. Tretyakov and M. Jansen, *J. Magn. Magn. Mater.*, 2008, **320**, 1068–1072.
- 24 A. Morisako, T. Naka, K. Ito, A. Takizawa, M. Matsumoto and Y. K. Hong, *J. Magn. Magn. Mater.*, 2002, **242–245**, 304–310.
- 25 P. Hernández, C. De Francisco, J. M. Muñoz, J. Iñiguez, L. Torres and M. Zazo, *J. Magn. Magn. Mater.*, 1996, **157–158**, 123–124.
- 26 Z. Jin, W. Tang, J. Zhang, H. Lin and Y. Du, *J. Magn. Magn. Mater.*, 1998, **182**, 231–237.
- 27 M. J. Iqbal, M. N. Ashiq, P. Hernandez-Gomez and J. M. Munoz, *J. Magn. Magn. Mater.*, 2008, **320**, 881–886.
- 28 B. T. Shirk and W. R. Buessem, *J. Am. Ceram. Soc.*, 1970, **53**, 192–196.
- 29 E. Alimohammadi, S. Sheibani and A. Ataie, *Mater. Chem. Phys.*, 2022, **275**, 125312.
- 30 R. C. Pullar, *Prog. Mater. Sci.*, 2012, **57**, 1191–1334.
- 31 F. Ansari, A. Sobhani and M. Salavati-Niasari, *J. Magn. Magn. Mater.*, 2016, **401**, 362–369.
- 32 A. Khoobi, M. Salavati-Niasari and O. Amiri, *J. Alloys Compd.*, 2021, **858**, 157745.
- 33 M. Laayati, A. Hasnaoui, N. Abdallah, S. Oubaassine, L. Fkhar, O. Mounkachi, S. El Houssame, M. Ait Ali and L. El Firdoussi, *J. Chem.*, 2020, 1–10.
- 34 M. Laayati, A. A. Mekkaoui, L. Fkhar, M. Ait Ali, H. Anane, L. Bahsis, L. El Firdoussi and S. El Houssame, *RSC Adv.*, 2022, **12**, 11139–11154.
- 35 Z. kheilkordi, G. Mohammadi Ziarani, S. Bahar and A. Badiei, *J. Iran. Chem. Soc.*, 2019, **16**, 365–372.
- 36 T. Ahmadi, G. Mohammadi Ziarani, S. M. Masoumian Hoseini, A. Badiei and M. M. Ranjbar, *J. Iran. Chem. Soc.*, 2021, **18**, 2047–2056.
- 37 F. Sanatkar, A. Khoobi and M. Salavati-Niasari, *Environ. Sci. Pollut. Res.*, 2021, **28**, 10791–10803.
- 38 M. Mahdiani, F. Soofivand, F. Ansari and M. Salavati-Niasari, *J. Cleaner Prod.*, 2018, **176**, 1185–1197.
- 39 P. C. A. Brito, R. F. Gomes, J. G. S. Duque and M. A. Macêdo, *Phys. B Condens. Matter*, 2006, **384**, 91–93.
- 40 A. Ghasemi and A. Morisako, *J. Magn. Magn. Mater.*, 2008, **320**, 1167–1172.
- 41 T. Chin, S. L. Hsu and M. C. Deng, *J. Magn. Magn. Mater.*, 1993, **120**, 64–68.
- 42 P. Sivakumar, L. Shani, Y. Yeshurun, A. Shaulov and A. Gedanken, *J. Mater. Sci.: Mater. Electron.*, 2016, **27**, 5707–5714.
- 43 Z. F. Zi, Y. P. Sun, X. B. Zhu, Z. R. Yang, J. M. Dai and W. H. Song, *J. Magn. Magn. Mater.*, 2008, **320**, 2746–2751.
- 44 R. A. Brand, *Normos Program, Internal Report, Angewandte Physik*, Universität Duisburg, 1987.
- 45 S. Wang, D. Li, Y. Xiao, W. Dang and J. Feng, *Russ. J. Phys. Chem. A*, 2017, **91**, 1981–1986.
- 46 M. A. P. Buzinaro, M. A. Macêdo, B. F. O. Costa and N. S. Ferreira, *Ceram. Int.*, 2019, **45**, 13571–13574.
- 47 J. Didari and A. Sadeghzadeh-Attar, *J. Taiwan Inst. Chem. Eng.*, 2021, **119**, 232–244.
- 48 T. P. Martin, R. Merlin, D. R. Huffman and M. Cardona, *Solid State Commun.*, 1977, **22**, 565–567.
- 49 N. Yang, H. Yang, J. Jia and X. Pang, *J. Alloys Compd.*, 2007, **438**, 263–267.
- 50 M. S. Chen, Z. X. Shen, X. Y. Liu and J. Wang, *J. Mater. Res.*, 2000, **15**, 483–487.
- 51 C. Akshayya, M. K. Okla, A. A. Al-ghamdi, S. A. Al-amri, A. A. Alatar, M. A. Abdel-Maksoud, M. Aufy and S. S. Khan, *J. Cluster Sci.*, 2023, **34**, 2459–2469.
- 52 J. Li, X. Zhang, Y. Chen, Y. Li, Y. Huang, Z. Du and T. Li, *Chin. Sci. Bull.*, 2005, **50**, 1044–1047.
- 53 S. Katlakunta, S. Singh, S. Srinath, M. Bououdina, R. Sandhya and K. Praveena, *Mater. Res. Bull.*, 2015, **63**, 58–66.
- 54 M. Manikandan, K. S. Kumar, N. Aparnadevi and C. Venkateswaran, *Phys. Status Solidi A*, 2015, **212**, 2179–2185.
- 55 F. Zan, N. Jabeen, W. Xiong, A. Hussain, Y. Wang and H. Xia, *Nanotechnology*, 2020, **31**, 185402.
- 56 T. Xie, L. Xu, C. Liu and Y. Wang, *Appl. Surf. Sci.*, 2018, **273**, 684–691.
- 57 B. D. Zdravkov, J. J. Čermák, M. Šefara and J. Janků, *Cent. Eur. J. Chem.*, 2007, **5**, 385–395.
- 58 S. Polarz and B. Smarsly, *J. Nanosci. Nanotechnol.*, 2002, **2**, 581–612.
- 59 A. J. Shnoudeh, I. Hamad, R. W. Abdo, L. Qadumii, A. Y. Jaber, H. S. Surchi and S. Z. Alkelany, *Biomater. Nanotechnol.*, 2019, 527–612.
- 60 R. A. Bepari, P. Bharali and B. K. Das, *J. Saudi Chem. Soc.*, 2017, **21**, S170–S178.
- 61 C. Huang, H. Zhang, Z. Sun, Y. Zhao, S. Chen, R. Tao and Z. Liu, *J. Colloid Interface Sci.*, 2011, **364**, 298–303.
- 62 Z. Pan, L. Hua, Y. Qiao, H. Yang, X. Zhao, B. Feng, W. Zhu and Z. Hou, *Chin. J. Catal.*, 2011, **32**, 428–435.
- 63 R. Y. Pawar and S. K. Pardeshi, *Arabian J. Chem.*, 2018, **11**, 282–290.
- 64 S. K. Pardeshi and R. Y. Pawar, *Mater. Res. Bull.*, 2010, **45**, 609–615.

