

CrossMark  
click for updatesCite this: *Chem. Sci.*, 2015, 6, 7213Received 5th June 2015  
Accepted 28th August 2015

DOI: 10.1039/c5sc02018b

www.rsc.org/chemicalscience

# Highly efficient, selective, and durable photocatalytic system for CO<sub>2</sub> reduction to formic acid†

Yusuke Tamaki,<sup>ab</sup> Kazuhide Koike<sup>c</sup> and Osamu Ishitani<sup>\*ab</sup>

We discovered an extremely suitable sacrificial electron donor, 1,3-dimethyl-2-(*o*-hydroxyphenyl)-2,3-dihydro-1*H*-benzo[*d*]imidazole, for the selective photocatalytic reduction of CO<sub>2</sub> to formic acid using a Ru(II)–Ru(II) supramolecular photocatalyst. The efficiency, durability, and rate of photocatalysis are significantly increased ( $\Phi_{\text{HCOOH}} = 0.46$ ,  $\text{TON}_{\text{HCOOH}} = 2766$ ,  $\text{TOF}_{\text{HCOOH}} = 44.9 \text{ min}^{-1}$ ) in comparison with those using 1,3-dimethyl-2-phenyl-2,3-dihydro-1*H*-benzo[*d*]imidazole or 1-benzyl-1,4-dihydronicotinamide.

## Introduction

A tremendous amount of carbon dioxide, the most oxidized form of carbon, has been produced from the combustion of carbon-containing materials such as fossil fuels, plastics, and foods. Because carbon dioxide is a primary greenhouse gas that contributes significantly toward global warming, the production of CO<sub>2</sub> must be reduced. Therefore, a technology that produces useful energy-rich chemicals from CO<sub>2</sub> with solar light as an energy source should be developed in the future.

Although hydrogen gas has garnered attention as a carbon-free fuel, it is constrained by its physical and chemical properties such as difficulties in transportation because of its low density and risk of explosion. Formic acid, one of the two-electron reduced compounds of CO<sub>2</sub>, is a promising hydrogen storage medium because it can easily be split by catalysts into hydrogen and CO<sub>2</sub> under mild conditions and it exists in the liquid form with a higher energy density at ambient temperature.<sup>1,2</sup> The hydrogenation reaction of CO<sub>2</sub> has been actively studied owing to its ability to produce formic acid.<sup>3–5</sup> For example, Himeda, Fujita, and co-workers recently reported iridium(III) catalysts for efficient hydrogenation of CO<sub>2</sub> under mild conditions.<sup>3</sup> Another method for the production of formic acid without H<sub>2</sub> is the photocatalytic reduction of CO<sub>2</sub>.

To the best of our knowledge, we were the first to report supramolecular photocatalysts for the selective reduction of

CO<sub>2</sub> to formic acid, which consist of [Ru(dmb)<sub>*m*</sub>(BL)<sub>3–*m*</sub>]<sup>2+</sup> (dmb = 4,4'-dimethyl-2,2'-bipyridine, BL = 1,2-bis(4'-methyl-[2,2'-bipyridin]-4-yl)ethane, *m* = 0, 1, 2) as a photosensitizer unit and [Ru(dmb)<sub>*n*</sub>(BL)<sub>2–*n*</sub>(CO)<sub>2</sub>]<sup>2+</sup> (*n* = 0, 1) as a catalyst unit.<sup>6</sup> In the photocatalytic reactions, a model compound of coenzyme NAD(P)H called 1-benzyl-1,4-dihydronicotinamide (BNAH, Chart 1) was employed as a sacrificial electron donor. In particular, a trinuclear complex with two photosensitizer units and one catalyst unit (**Ru<sub>2</sub>–Ru(CO)**, Chart 1) exhibited the highest photocatalytic activity. A high turnover number ( $\text{TON}_{\text{HCOOH}} = 671$ ) and turnover frequency ( $\text{TOF}_{\text{HCOOH}} = 11.6 \text{ min}^{-1}$ ) for the formation of formic acid were observed. However, the quantum yield for formic acid formation was relatively low ( $\Phi_{\text{HCOOH}} = 0.061$ ), even compared with that for supramolecular photocatalytic systems employing the same photosensitizer units and *cis,trans*-[Re(BL)(CO)<sub>2</sub>(L)<sub>2</sub>]<sup>2+</sup>-type complexes as catalyst units. These systems selectively produced CO, with  $\Phi_{\text{CO}}$  values ranging from 0.10 to 0.15.<sup>7</sup>

We also reported that BNAH has several disadvantages as a sacrificial electron donor for the improvement of photocatalysis in supramolecular systems.<sup>6–8</sup> First, the efficiency of quenching the excited state of the Ru(II) photosensitizer unit with BNAH is relatively low. For example, even a 0.1 M solution of BNAH quenched only 59% of the excited photosensitizer unit in **Ru<sub>2</sub>–Ru(CO)**. Second, a relatively fast back electron transfer occurs from the reduced form of the photosensitizer unit to the oxidized form of BNAH, *i.e.*, BNAH<sup>•+</sup>. Third, accumulation of the BNA dimers (BNA<sub>2</sub>), which were produced from the deprotonation of BNAH<sup>•+</sup> and following coupling processes, prevents further progression of the photocatalytic reaction. This is because BNA<sub>2</sub> is more effective than BNAH at quenching the excited photosensitizer unit of the supramolecular photocatalysts. Owing to these limitations, we can conclude that the reported values of the photocatalytic abilities of **Ru<sub>2</sub>–Ru(CO)** do not reflect their actual potential.

<sup>a</sup>Department of Chemistry, Graduate School of Science and Engineering, Tokyo Institute of Technology, 2-12-1-NE-1 O-okayama, Meguro-ku, Tokyo, 152-8550, Japan. E-mail: ishitani@chem.titech.ac.jp

<sup>b</sup>CREST, Japan Science and Technology Agency, 4-1-8 Honcho, Kawaguchi-city, Saitama, 322-0012, Japan

<sup>c</sup>National Institute of Advanced Industrial Science and Technology, Onogawa 16-1, Tsukuba 305-8569, Japan

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c5sc02018b





Chart 1 Structures and abbreviations of  $\text{Ru}_2\text{-Ru(CO)}$ , model mononuclear complexes,  $\text{BI(OH)H}$ ,  $\text{BIH}$ , and  $\text{BNAH}$ . The counter anions of the complexes were  $\text{PF}_6^-$ .

We recently discovered that compared with  $\text{BNAH}$ , a benzimidazole derivative ( $\text{BIH}$ , Chart 1) can function as a much better sacrificial electron donor for the excited state of  $[\text{Ru}(\text{N}^{\wedge}\text{N})_3]^{2+}$ -type ( $\text{N}^{\wedge}\text{N}$  = diimine ligand) complexes.<sup>8</sup> The efficiency, durability, and formation rate of  $\text{CO}$  generated from the photocatalytic reduction of  $\text{CO}_2$  with the  $\text{Ru(II)-Re(I)}$  supramolecular photocatalyst ( $\text{Ru-Re}$ ) were substantially improved with  $\text{BIH}$  ( $\Phi_{\text{CO}} = 0.45$ ,  $\text{TON}_{\text{CO}} = 3029$ ,  $\text{TOF}_{\text{CO}} = 35.7 \text{ min}^{-1}$ ) compared to those with  $\text{BNAH}$  ( $\Phi_{\text{CO}} = 0.15$ ,  $\text{TON}_{\text{CO}} = 207$ ,  $\text{TOF}_{\text{CO}} = 4.7 \text{ min}^{-1}$ ).  $\text{BIH}$  could quantitatively quench the excited state of the  $\text{Ru(II)-Re(I)}$  photocatalyst.  $\text{BIH}$  is more effective than  $\text{BNAH}$  in decreasing the efficiency of the back electron transfer from its oxidized form to the reduced form of the photocatalyst.  $\text{BIH}$  serves as a two-electron donor, whereas  $\text{BNAH}$  can only donate one electron to the photocatalyst because of the coupling reaction of  $\text{BNA}^{\cdot}$ . The two-electron oxidized product of  $\text{BIH}$  ( $\text{BI}^+$ ) did not prevent the progress of the photocatalytic reaction.

We applied similar strategies in this study and implemented a new reductant to clarify the “real” photocatalytic abilities of  $\text{Ru}_2\text{-Ru(CO)}$  for the reduction of  $\text{CO}_2$ . We found that the photocatalysis of  $\text{Ru}_2\text{-Ru(CO)}$  is significantly better than those employing  $\text{BNAH}$  or  $\text{BIH}$  if another benzimidazole derivative with an  $-\text{OH}$  group at the *o*-position of the phenyl group, *i.e.*, 1,3-dimethyl-2-(*o*-hydroxyphenyl)-2,3-dihydro-1*H*-benzo[*d*]imidazole<sup>9-12</sup> ( $\text{BI(OH)H}$ , Chart 1), is used. In particular, this method gave the highest rate for the photocatalytic reduction of  $\text{CO}_2$  of all previously reported visible-light-driven photocatalytic systems ( $\text{TOF}_{\text{HCOOH}} = 44.9 \text{ min}^{-1}$ ).

## Results

We determined the quantum yield ( $\Phi$ ), turnover number ( $\text{TON}$ ), and turnover frequency ( $\text{TOF}$ ) of the reduction product(s) to evaluate the photocatalysts. The following reaction conditions were selected. The details and justifications for these conditions are described in ESI.<sup>†</sup>

Light irradiation condition 1 ( $\text{LIC1}$ ) was used to determine the  $\Phi_{\text{HCOOH}}$ : a 480 nm monochromatic light with  $5.0 \times 10^{-9}$  einstein  $\text{s}^{-1}$  intensity was used for excitation. Quantum yields were determined using two different concentrations of the photocatalyst, *i.e.*, 0.15 mM and 0.025 mM. When  $[\text{Ru}_2\text{-Ru(CO)}]$

was 0.15 mM, the absorbance of the solution was greater than 3 with a 1 cm path length. The solution was mixed vigorously during the irradiation process. Using 0.025 mM  $\text{Ru}_2\text{-Ru(CO)}$ , the number of absorbed photons could be calculated from the change in absorbance at 480 nm during irradiation.

$\text{LIC2}$  was used for determining the  $\text{TON}_{\text{HCOOH}}$ : a wavelength of light  $>500 \text{ nm}$  was used for excitation. The photocatalyst concentration was 0.025 mM.

$\text{LIC3}$  was used for determining the  $\text{TOF}_{\text{HCOOH}}$ : a wavelength of light  $>420 \text{ nm}$  was used for excitation. The photocatalyst concentration was 0.025 mM.

Fig. 1 shows the UV-vis absorption spectra of the reductants,  $\text{BIH}$  and  $\text{BI(OH)H}$ , and their respective oxidized compounds,  $\text{BI}^+$  and  $\text{BI(O}^{\ominus})^+$  along with the photocatalyst,  $\text{Ru}_2\text{-Ru(CO)}$ . Because none of these compounds absorbed wavelength of light longer than 440 nm, the excitation light was selectively absorbed by  $\text{Ru}_2\text{-Ru(CO)}$  in the  $\text{LIC1}$  and  $\text{LIC2}$  conditions in a mixed solvent system of *N,N*-dimethylformamide (DMF) and triethanolamine (TEOA) (4 : 1 v/v), which was also used as the solvent in the photocatalytic reactions. Because the irradiated light was partially absorbed by  $\text{BI(O}^{\ominus})^+$  in  $\text{LIC3}$ , the  $\text{TOF}_{\text{HCOOH}}$  values were obtained in the first stage of the photocatalytic reaction when only a small amount of  $\text{BI(O}^{\ominus})^+$  had accumulated in the reaction solution (10 min irradiation).

We first attempted to use  $\text{BIH}$  as a reductant. A mixed solution of DMF and TEOA (4 : 1 v/v) containing  $\text{Ru}_2\text{-Ru(CO)}$  (0.025 mM) and  $\text{BIH}$  (0.1 M) was irradiated ( $>500 \text{ nm}$ ,  $\text{LIC2}$ ) under a  $\text{CO}_2$  atmosphere. The resulting photocatalytic products



Fig. 1 UV-vis absorption spectra of  $\text{BIH}$  (black solid line),  $\text{BI}^+$  (black broken line),  $\text{BI(OH)H}$  (red solid line),  $\text{BI(O}^{\ominus})^+$  (red broken line), and  $\text{Ru}_2\text{-Ru(CO)}$  (blue line, 1/10 intensity) in DMF-TEOA (4 : 1 v/v).



Table 1 Photocatalytic properties using  $\text{Ru}_2\text{-Ru}(\text{CO})^a$ 

Reductant	TON <sup>b</sup> (selectivity <sup>c</sup> /%)			$\Phi_{\text{HCOOH}}^d$		TOF <sub>HCOOH</sub> <sup>e</sup> /min <sup>-1</sup>	$k_q^f$ /10 <sup>8</sup> M <sup>-1</sup> s <sup>-1</sup>	$\eta_q^g$
	HCOOH	CO	H <sub>2</sub>	0.15 mM	0.025 mM			
BI(OH)H	2766 (87)	215 (7)	212	0.46	0.42	44.9	9.9	0.99
BIH	641 (72)	237 (27)	13	0.18	0.17	10.2	11.0	0.99
BNAH	562 (91)	29 (5)	29	0.06	0.04	7.8	0.20	0.59

<sup>a</sup> A CO<sub>2</sub> saturated DMF-TEOA (4 : 1 v/v) solution consisting of a sacrificial electron donor (0.1 M) and  $\text{Ru}_2\text{-Ru}(\text{CO})$  was irradiated. The concentration of  $\text{Ru}_2\text{-Ru}(\text{CO})$  was 0.15 mM or 0.025 mM for the measurement of  $\Phi$  (LIC1) and 0.025 mM for the measurement of TON and TOF (LIC2 and LIC3, respectively). <sup>b</sup> A 2 mL solution was irradiated in LIC2 for 20 h. <sup>c</sup> Selectivity of the products. <sup>d</sup> A 4 mL solution was irradiated using LIC1 (light intensity:  $5.0 \times 10^{-9}$  einstein s<sup>-1</sup>). <sup>e</sup> A 4 mL solution was irradiated using LIC3. <sup>f</sup> Quenching rate constant of emission from the photosensitizer unit by a sacrificial electron donor. <sup>g</sup> Quenching fractions of emission, which is calculated as  $\eta_q = k_q \tau_{\text{em}} [\text{reductant}] / (1 + k_q \tau_{\text{em}} [\text{reductant}])$ , from the photosensitizer unit using 0.1 M of a sacrificial electron donor, where the emission lifetime of  $\text{Ru}_2\text{-Ru}(\text{CO})$  ( $\tau_{\text{em}}$ ) was 726 ns (ref. 6).

included both formic acid (TON<sub>HCOOH</sub> = 641) and CO (TON<sub>CO</sub> = 237). Note that the substitution of BIH with BNAH under this same reaction condition gives formic acid as a main product and CO as an extremely minor product (TON<sub>HCOOH</sub> = 562, TON<sub>CO</sub> = 29). Therefore, the yield for the selective formation of formic acid decreased from 91% to 72% when BIH was used as the reductant (Table 1). Markedly, BIH could function as a fascinating sacrificial electron donor for CO<sub>2</sub> reduction with  $\text{Ru-Re}$  to give CO as the main product ( $\Phi_{\text{CO}} = 0.45$ , TON<sub>CO</sub> = 3029, TOF<sub>CO</sub> = 35.7 min<sup>-1</sup>). These values are substantially greater than those obtained with BNAH.<sup>8</sup>

The total reaction scheme for the photocatalytic reduction of CO<sub>2</sub> to CO using  $\text{Ru-Re}$  and BIH was reported as follows.



The formation of formic acid from CO<sub>2</sub> might require two protons along with the two required electrons. This may induce a shortage of protons in the solution during the photocatalytic reaction process.



Therefore, we substituted the reductant BIH with another benzimidazole derivative with an OH group, BI(OH)H,<sup>13</sup> which can supply two electrons and two protons from one molecule.<sup>9-11</sup> This substitution of BIH with BI(OH)H using the same photochemical reaction condition (LIC2) produced formic acid with a much higher TON (TON<sub>HCOOH</sub> = 2766) and selectivity (87%) (eqn (1), Fig. 2a). When  $\text{Ru}_2\text{-Ru}(\text{CO})$  or irradiation was excluded from the experimental condition, no formic acid was produced. The amount of formic acid produced during the photocatalytic reaction without TEOA (TON<sub>HCOOH</sub> = 1096 after 8 h irradiation) was lower than that with TEOA (TON<sub>HCOOH</sub> = 1504) (Fig. S2†). Using a mixed system of model complexes (Chart 1), *i.e.*, [Ru(dmb)<sub>3</sub>]<sup>2+</sup> ( $\text{Ru}$ , dmb = 4,4'-dimethyl-2,2'-bipyridine) and *cis*-[Ru(dmb)<sub>2</sub>(CO)<sub>2</sub>]<sup>2+</sup> ( $\text{Ru}(\text{CO})$ ), both the TON (TON<sub>HCOOH</sub> = 1969) and the selectivity (78%) of formic acid formation were also lower than those using  $\text{Ru}_2\text{-Ru}(\text{CO})$  (Fig. 2b). The quantum yields for formic acid formation exhibited very high values;  $\Phi_{\text{HCOOH}} = 0.46$  with [Ru<sub>2</sub>-Ru(CO)] = 0.15 mM and  $\Phi_{\text{HCOOH}} = 0.42$  with [Ru<sub>2</sub>-Ru(CO)] = 0.025 mM. The reaction rate was also very high (TOF<sub>HCOOH</sub> = 44.9 min<sup>-1</sup>). To the best of our knowledge, the turnover frequency value in particular is the highest of those reported for visible-light-driven photocatalysts for CO<sub>2</sub> reduction. As shown in Fig. 2b


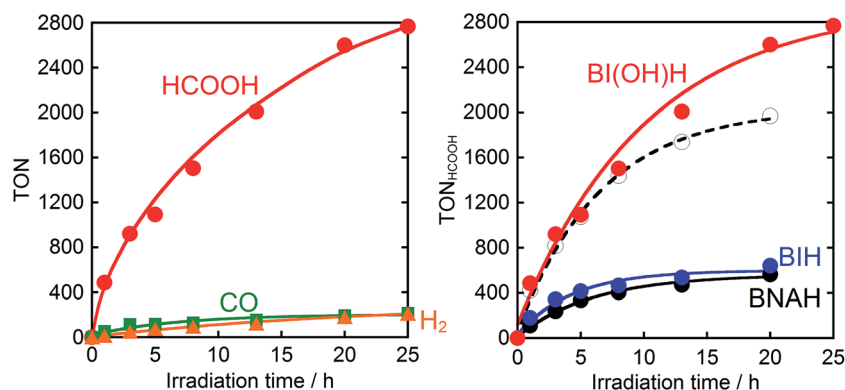


Fig. 2 (a) Photocatalytic formation of formic acid (●), CO (■), and H<sub>2</sub> (▲) as a function of irradiation time. (b) Photocatalytic formation of formic acid using BI(OH)H (●), BIH (●) or BNAH (●) as a sacrificial electron donor: a CO<sub>2</sub> saturated DMF-TEOA (4 : 1 v/v, 2 mL) solution containing  $\text{Ru}_2\text{-Ru}(\text{CO})$  (0.025 mM) and a sacrificial electron donor (0.1 M) was irradiated using  $\lambda_{\text{ex}} > 500$  nm light (LIC2). Open circles (c) show the results obtained from the photocatalysis using BI(OH)H (0.1 M) and a mixed system of [Ru(dmb)<sub>3</sub>]<sup>2+</sup> (0.05 mM) and *cis*-[Ru(dmb)<sub>2</sub>(CO)<sub>2</sub>]<sup>2+</sup> (0.025 mM) instead of  $\text{Ru}_2\text{-Ru}(\text{CO})$ .



and Table 1, the previously described photocatalysis of  $\text{Ru}_2\text{-Ru(CO)}$  significantly increased when  $\text{BI(OH)H}$  was used instead of  $\text{BIH}$  or  $\text{BNAH}$ .



In the photoinduced electron transfer process, the quenching rate constant of emission from the photosensitizer unit of  $\text{Ru}_2\text{-Ru(CO)}$  by  $\text{BI(OH)H}$  ( $k_q = 9.9 \times 10^8 \text{ M}^{-1} \text{ s}^{-1}$ ) was significantly larger than that by  $\text{BNAH}$  ( $k_q = 2.0 \times 10^7 \text{ M}^{-1} \text{ s}^{-1}$ ). This result is reasonable because  $\text{BI(OH)H}$  ( $E_{1/2}(\text{BI(OH)H}/\text{BI(OH)H}^+) = -0.06 \text{ V}$ )<sup>12</sup> is a better reducing agent than  $\text{BNAH}$  ( $E^\circ(\text{BNAH}/\text{BNAH}^+) = 0.20 \text{ V}$ ).<sup>14</sup> Under photocatalytic reaction conditions where the  $[\text{reductant}] = 0.1 \text{ M}$ , the reductive quenching by  $\text{BI(OH)H}$  proceeded almost quantitatively ( $\eta_q = 99\%$ ) and was 1.7 times more efficient than that by  $\text{BNAH}$  ( $\eta_q = 59\%$ ). This could be one of the reasons  $\text{BI(OH)H}$  provides a higher photocatalytic efficiency than  $\text{BNAH}$ .<sup>15</sup>

A labeling experiment using  $^{13}\text{CO}_2$  was conducted to determine the source of the carbon atoms in the produced formic acid. Prior to irradiation, a strong signal attributed to  $^{13}\text{CO}_2$  was observed at 125.6 ppm in a  $^{13}\text{C}\{^1\text{H}\}$  NMR spectrum of a  $\text{DMF-}d_7\text{-TEOA}$  (4 : 1 v/v) solution consisting of  $\text{Ru}_2\text{-Ru(CO)}$  (0.5 mM) and  $\text{BI(OH)H}$  (0.1 M) under a  $^{13}\text{CO}_2$  (569 mmHg) atmosphere (Fig. 3a). Irradiation at  $\lambda_{\text{ex}} > 420 \text{ nm}$  for 13.5 h caused both a decrease in the  $^{13}\text{CO}_2$  signal and appearance of a strong signal at 168.2 ppm, which was attributed to an equilibrium mixture of  $\text{H}^{13}\text{COOH}$  and  $\text{H}^{13}\text{COO}^-$  (Fig. 3b). In the  $^1\text{H}$  NMR spectrum of the same solution, a doublet ( $^1J_{\text{CH}} = 188 \text{ Hz}$ ) at 8.52 ppm was attributed to the proton of an equilibrium mixture of  $\text{H}^{13}\text{COOH}$  and  $\text{H}^{13}\text{COO}^-$ , which should be coupled with the  $^{13}\text{C}$  atom. The peak area of a singlet at 8.52 ppm was approximately 1/100 of the peak area of the doublet and was attributed to the equilibrium mixture of  $\text{H}^{12}\text{COOH}$  and  $\text{H}^{12}\text{COO}^-$  (Fig. 4). This peak area ratio was consistent with the contamination of  $^{12}\text{CO}_2$  in the used  $^{13}\text{CO}_2$  (99%). The same  $J$  value from the  $^{13}\text{C}$ -H coupling (188 Hz) was also observed in the  $^{13}\text{C}$  NMR spectrum that was measured without  $^1\text{H}$  decoupling (Fig. 5). These results clearly show that formic acid was produced through the reduction of  $\text{CO}_2$ .

The simultaneous consumption of  $\text{BI(OH)H}$  and the production of its oxidized compound during the photocatalytic reaction were quantitatively analyzed by high-performance liquid chromatography (HPLC). The oxidized compound of  $\text{BI(OH)H}$ , a two-electron oxidized and two-proton releasing compound ( $\text{BI(O}^-\text{)}^+$ ), was quantitatively produced (eqn (2)).



Fig. 6 shows that the amounts of consumed  $\text{BI(OH)H}$  and the generated  $\text{BI(O}^-\text{)}^+$ , and the sum of the generated two-electron reduced compounds (formic acid +  $\text{CO}$  +  $\text{H}_2$ ) were almost



Fig. 3  $^{13}\text{C}\{^1\text{H}\}$  NMR spectra of the reaction solution before (a) and after (b) 13.5 h of irradiation:  $\text{DMF-}d_7\text{-TEOA}$  (4 : 1 v/v) solution containing  $\text{BI(OH)H}$  (0.1 M),  $\text{Ru}_2\text{-Ru(CO)}$  (0.5 mM), and  $^{13}\text{CO}_2$  (569 mmHg) was irradiated at  $>420 \text{ nm}$  using a xenon lamp.



Fig. 4  $^1\text{H}$  NMR spectrum after 13.5 h irradiation for the same sample shown in Fig. 3.



Fig. 5  $^{13}\text{C}$  NMR spectrum without  $^1\text{H}$  decoupling after 13.5 h irradiation for the same sample shown in Fig. 3.

equivalent. For example, after a 3 h irradiation period, 55  $\mu\text{mol}$  of  $\text{BI(OH)H}$  was consumed and 54  $\mu\text{mol}$  of  $\text{BI(O}^-\text{)}^+$  and 54  $\mu\text{mol}$  of the two-electron reduced compounds were produced. Therefore, it is clear that  $\text{BI(OH)H}$  acts as both a two-electron donor and a two-proton donor, and the electrons and material balances in the photocatalytic reaction can be represented in eqn (3). Moreover, it should be noted that although  $\text{BIH}$  functions as a two-electron donor, only one proton was released in the two-electron oxidation process (eqn (4)).<sup>8</sup>



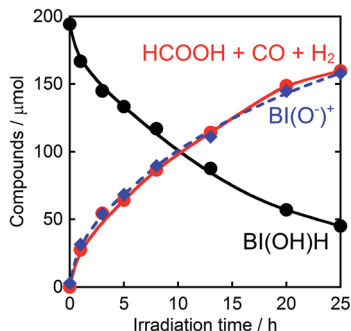


Fig. 6 Photocatalytic production of the reduction products (HCOOH + CO + H<sub>2</sub>, ●) and BI(O<sup>-</sup>)<sup>+</sup> (◆), and the consumption of BI(OH)H (●): a CO<sub>2</sub> saturated DMF–TEOA (4 : 1 v/v, 2 mL) solution containing BI(OH)H (0.1 M) and Ru<sub>2</sub>–Ru(CO) (0.025 mM) was irradiated using λ<sub>ex</sub> > 500 nm light (LIC2).



To clarify the two-electron donation processes of BI(OH)H, a laser flash photolysis method was employed. A DMF–TEOA mixed solution containing BI(OH)H (0.1 M) and Ru (0.3 mM), which was used as a model of the photosensitizer unit, was irradiated at λ<sub>ex</sub> = 532 nm using a Nd:YAG pulse laser. The time-resolved UV-vis absorption spectrum is shown in Fig. 7. At 100 ns after the laser excitation, new absorption was observed at 500–550 nm. This is attributed to the one-electron reduced species of Ru, *i.e.*, Ru<sup>-</sup>,<sup>8</sup> which should be produced *via* the reductive quenching of excited Ru by BI(OH)H. Fig. 8 shows the time course of [Ru<sup>-</sup>] measured at λ<sub>abs</sub> = 550 nm, which increased in two steps. The initial rapid increase was completed within the laser pulse, and the concentration of Ru<sup>-</sup> increased up to approximately 10 μs. These results clearly indicate that BI(OH)H acts as a two-electron donor with one-photon excitation of Ru. Since BI(OH)<sup>•</sup>, which can be produced *via* the deprotonation of BI(OH)H<sup>•+</sup>, has strong reducing power ( $E_{\text{p}}^{\text{ox}} = -1.96 \text{ V vs. Fe}^+/\text{Fe}$ ),<sup>12</sup> it should be able to donate an electron to another Ru molecule even in the ground state ( $E_{1/2}^{\text{red}} = -1.81 \text{ V}$ ).



Fig. 7 Time-resolved UV-vis absorption spectrum at 100 ns after the laser excitation: a DMF–TEOA (5 : 1 v/v) solution containing Ru (0.3 mM) and BI(OH)H (0.1 M) was irradiated at λ<sub>ex</sub> = 532 nm with a Nd:YAG pulse laser under degassed conditions at room temperature.

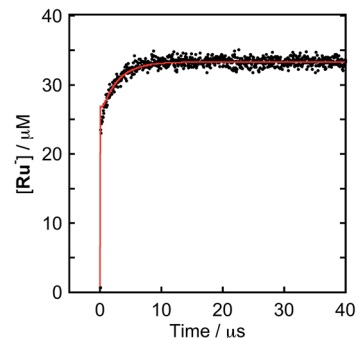



Fig. 8 Formation of Ru<sup>-</sup>: (a) DMF–TEOA (5 : 1 v/v) solution containing Ru (0.3 mM) and BI(OH)H (0.1 M) was irradiated at λ<sub>ex</sub> = 532 nm with a Nd:YAG pulse laser under degassed conditions at room temperature. The red line shows the fitting results (ESI†).

This time course of the Ru<sup>-</sup> production was fitted using numerical analysis based on kinetics, as shown in Scheme 1,<sup>8</sup> where  $I_0$  is the light intensity absorbed by Ru, <sup>1</sup>(\*Ru) and <sup>3</sup>(\*Ru) are singlet and triplet metal-to-ligand charge-transfer (MLCT) excited states of Ru, respectively, (Ru<sup>-</sup>···BI(OH)H<sup>•+</sup>) is an ion pair produced *via* the reductive quenching of <sup>3</sup>(\*Ru) by BI(OH)H, and B is a base, *i.e.*, TEOA or BI(OH)H. The quenching rate constant of <sup>3</sup>(\*Ru) was obtained with a Stern–Volmer analysis of emission from <sup>3</sup>(\*Ru) ( $k_{\text{q}} = 1.17 \times 10^9 \text{ M}^{-1} \text{ s}^{-1}$ ). The increase in Ru<sup>-</sup> was fitted using eqn (5), for which the derivation is shown in the ESI.†

$$\frac{d[\text{Ru}^-]}{dt} = k_{\text{esc}}[(\text{Ru}^- \cdots \text{BI}(\text{OH})\text{H}^{\bullet+})] + k_{\text{et}}[\text{Ru}][\text{BI}(\text{OH})^{\bullet}] - k_{\text{rec2}}[\text{Ru}^-][\text{BI}(\text{OH})\text{H}^{\bullet+}] \quad (5)$$

Based on these analyses, the rate constants of the electron transfer from BI(OH)<sup>•</sup> to the ground state of Ru ( $k_{\text{et}}$ ), of the back electron transfer from Ru<sup>-</sup> to BI(OH)H<sup>•+</sup> ( $k_{\text{rec2}}$ ), and of the deprotonation of BI(OH)H<sup>•+</sup> ( $k_{\text{dp}}$ ) were  $9 \times 10^9 \text{ M}^{-1} \text{ s}^{-1}$ ,  $5 \times 10^9 \text{ M}^{-1} \text{ s}^{-1}$ , and  $2 \times 10^5 \text{ s}^{-1}$ , respectively.

The formation quantum yields for the one-electron-reduced species (OERS) ( $\Phi_{\text{OERS}}$ ) of the model of the photosensitizer unit, Ru, using BI(OH)H, BIH, and BNAH were also determined to compare their abilities as sacrificial electron donors (Table 2). A DMF–TEOA (5 : 1 v/v) solution containing Ru (0.1 mM) and one

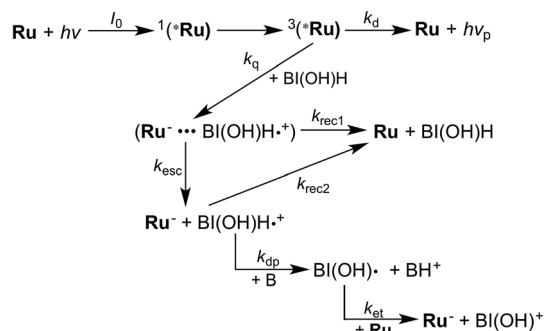

Scheme 1 Kinetics of Ru<sup>-</sup> production using BI(OH)H.



**Table 2** The accumulation quantum yields of OERS of Ru using BI(OH)H, BIH, or BNAH as a reductant<sup>a</sup>


Light intensity / $10^{-9}$ einstein $s^{-1}$	$\Phi_{\text{OER}}$		
	BI(OH)H	BIH	BNAH
11	0.45	0.59	0.066
4.3	0.54	0.74	0.087
1.1	0.64	0.95	0.14

<sup>a</sup> A 4 mL Ar-saturated DMF-TEOA (5 : 1 v/v) solution consisting of the reductant (0.1 M) and Ru (0.1 mM) was irradiated at 480 nm.




of the reductants (0.1 M) was irradiated with three different light intensities. The production of  $\text{Ru}^-$  was monitored with a UV-vis absorption spectrometer. A greater light intensity induced a lower quantum yield in all cases (Table 2). Irradiation with a greater light intensity should result in higher concentrations of both  $\text{Ru}^-$  and the one-electron oxidized species of the reductant ( $\text{QH}^+$ ). This should, in turn, induce more rapid back electron transfer from  $\text{Ru}^-$  to  $\text{QH}^+$ . When BI(OH)H was used as the reductant, the values of  $\Phi_{\text{OER}}$  were 5–7 times greater than those by using BNAH. This ratio is consistent with the quantum yields of production for formic acid, *i.e.*,  $\Phi_{\text{HCOOH}}(\text{BI(OH)H})/\Phi_{\text{HCOOH}}(\text{BNAH}) = 7.7$  with a light intensity of  $5.0 \times 10^{-9}$  einstein  $s^{-1}$  (LIC1). Therefore, the main reasons for the significant increase in the  $\Phi_{\text{HCOOH}}$  value when BI(OH)H is substituted for BNAH are ascribed to an increase in the electron-donating ability and suppression of the back electron transfer (Table 2 and Fig. 7).<sup>8</sup>

## Discussion

From the steady-state measurements of BI(OH)H decay and  $\text{BI(O}^-)^+$  formation and the transient measurement of  $\text{Ru}^-$  by laser flash photolysis, we can conclude that BI(OH)H acts as a two-electron donor with one-photon excitation of  $\text{Ru}_2\text{-Ru(CO)}$  during photocatalysis. As the initial process, excited  $\text{Ru}_2\text{-Ru(CO)}$  was reductively quenched by BI(OH)H giving the OERS of the photosensitizer unit and  $\text{BI(OH)H}^{+\bullet}$  at a rate constant of  $k_q = 9.9 \times 10^8 \text{ M}^{-1} \text{ s}^{-1}$ , which was obtained from linear Stern-Volmer plots (Fig. 9, eqn (6)). The second step is most likely the deprotonation of  $\text{BI(OH)H}^{+\bullet}$  by a base (B), *i.e.*, TEOA or BI(OH)H to produce  $\text{BI(OH)}^\bullet$  (eqn (7)). The intramolecular electron transfer should occur from the OERS of the photosensitizer unit to the catalyst unit (eqn (8)). Because  $\text{BI(OH)}^\bullet$  is a strong reducing agent, it can donate an additional electron to  $\text{Ru}_2\text{-Ru(CO)}$  ( $E_{1/2}^{\text{red}} = -1.87 \text{ V}$ ) and/or possibly to a reaction intermediate derived from the OERS of  $\text{Ru}_2\text{-Ru(CO)}$  ( $\text{Ru}_2\text{-Ru(Intermediate)}$ , eqn (10)) in the ground state (eqn (9) and (12)). Excitation of the photosensitizer unit of  $\text{Ru}_2\text{-Ru(Intermediate)}$  might allow the acceptance of an additional electron from BI(OH)H (eqn (11)). In the last step,  $\text{BI(OH)}^\bullet$  should release an additional proton to produce a zwitterion  $\text{BI(O}^-)^+$  as a dead-end oxidized compound of BI(OH)H (eqn (13)). Therefore, a single-photon excitation of  $\text{Ru}_2\text{-Ru(CO)}$  should allow BI(OH)H to donate two electrons and two protons *via* a sequence of electron transfer, deprotonation, electron transfer, and deprotonation processes.

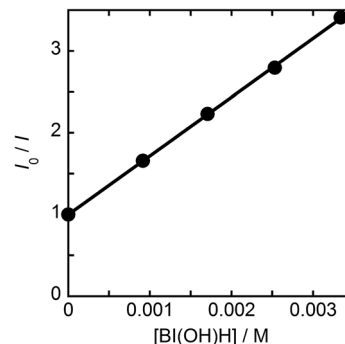

**Fig. 9** Stern-Volmer plots of emission quenching of  $\text{Ru}_2\text{-Ru(CO)}$  by BI(OH)H in DMF-TEOA (4 : 1 v/v); the excitation wavelength was 530 nm.

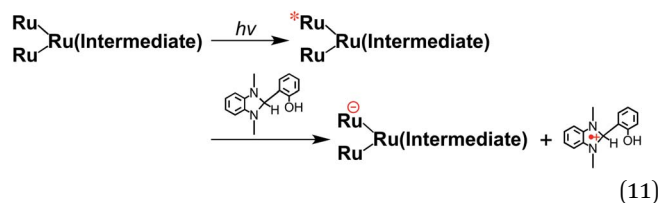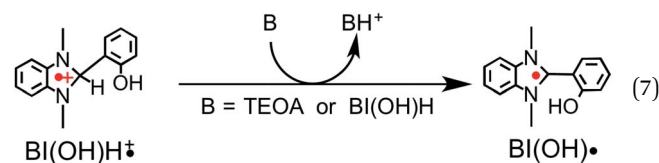



As described above, the photocatalytic  $\text{CO}_2$  reduction to formic acid proceeded using BI(OH)H without TEOA; however the  $\text{TON}_{\text{HCOOH}}$  was lower than that using BI(OH)H with TEOA (Fig. S2†). As previously reported, TEOA does not quench the  $^3\text{MLCT}$  excited state of the photosensitizer unit of  $\text{Ru}_2\text{-Ru(CO)}$ , which means that it should function only as a base in the photocatalytic reaction. In the absence of TEOA, a proton from  $\text{BI(OH)}^+$  should be captured by another molecule of BI(OH)H. Since the rates of the deprotonation process of  $\text{BI(OH)}^+$  and the back electron transfer process from the OERS of  $\text{Ru}_2\text{-Ru(CO)}$  to  $\text{BI(OH)}^+$  compete with each other (Scheme 1), slower deprotonation should lower the electron-donating ability of BI(OH)H.

Although BIH has a slightly stronger electron-donating ability than BI(OH)H (Table 2),  $\Phi_{\text{HCOOH}}$  and the selectivity toward the formation of formic acid using BIH were both significantly lower than those in the case of BI(OH)H (Table 1). As previously reported, a system that used both  $\text{Ru-Re}$  as the photocatalyst and BIH as the reductant showed an extremely high efficiency, durability, and rate for the photocatalytic reduction of  $\text{CO}_2$  ( $\Phi_{\text{CO}} = 0.45$ ,  $\text{TON}_{\text{CO}} = 3029$ ).<sup>8</sup> A system that utilized  $\text{Ru}_2\text{-Ru(CO)}$  as the photocatalyst and BIH as the electron donor showed an eight-fold increase in the production of CO ( $\text{TON}_{\text{CO}} = 237$ ), whereas the amount of formic acid ( $\text{TON}_{\text{HCOOH}} = 641$ ) was almost equivalent to the results obtained with BNAH ( $\text{TON}_{\text{CO}} = 29$ ,  $\text{TON}_{\text{HCOOH}} = 562$ ). As

described above, the difference between BI(OH)H and BIH is most likely attributed to the number of released protons per donated electrons. A one-photon excitation of  $\text{Ru}_2\text{-Ru(CO)}$  allows BI(OH)H to donate two electrons and two protons (eqn (2)) in a step-by-step process. Conversely, BIH can only donate two electrons and one proton (eqn (4)).<sup>8</sup> In the case of BNAH, only one electron and one proton can be donated (eqn (14)), where the ratio between the donated electron and proton is similar to BI(OH)H.<sup>6,7</sup> In other words, BIH can only donate half the amount of protons for every electron; however, both BI(OH)H and BNAH can donate an equal amount of protons for every electron.



To determine the effects of the proton concentration in the solution on the photocatalysis of  $\text{Ru}_2\text{-Ru(CO)}$ , a photocatalytic reaction that uses BIH in the presence of a phenol (0.1 M) as a proton source was investigated (Fig. 10). In the initial stage of the photocatalytic reaction (1 h irradiation), the TONs for formic acid and CO were 406 and 122, respectively. This is similar to a system containing BI(OH)H ( $\text{TON}_{\text{HCOOH}} = 484$ ,  $\text{TON}_{\text{CO}} = 53$ ), where the  $\text{TON}_{\text{HCOOH}}$  is 2.3 times larger than a system with BIH ( $\text{TON}_{\text{HCOOH}} = 180$ ,  $\text{TON}_{\text{CO}} = 46$ ). This result clearly indicates that BIH decreases the formation of formic acid, which is caused by a shortage of protons as BIH can only supply half the amount of protons for every donated electron but conversion of  $\text{CO}_2$  to HCOOH requires both two electrons and two protons.<sup>16,17</sup>

Candidates for the  $\text{Ru}_2\text{-Ru(Intermediate)}$  might be formate and carboxylato complexes as the catalyst unit, *i.e.*,  $[\text{Ru}(\text{BL})_2\text{(CO)}(\text{OC}(\text{O})\text{H})]^{18}$  and  $[\text{Ru}(\text{BL})_2\text{(CO)}(\text{COOH})]^{19}$  (eqn (10)). Sullivan, Meyer, and co-workers reported an electrocatalytic reduction of  $\text{CO}_2$  to formic acid using the hydrido complex *cis*- $[\text{Ru}(\text{bpy})_2(\text{CO})\text{H}]^+$  (bpy = 2,2'-bipyridine).<sup>18</sup> They suggested that the one-electron reduction of *cis*- $[\text{Ru}(\text{bpy})_2(\text{CO})\text{H}]^+$  and the subsequent insertion of  $\text{CO}_2$  gives *cis*- $[\text{Ru}(\text{bpy})_2(\text{CO})(\text{OC}(\text{O})\text{H})]^0$ . A subsequent additional electron reduction leads to the loss of the formate anion and *cis*- $[\text{Ru}(\text{bpy})_2(\text{CO})\text{H}]^+$  is reformed. If a similar mechanism occurs in the photocatalytic reaction of  $\text{Ru}_2\text{-Ru(CO)}$ , the formation of the hydrido complex might become more favorable if BI(OH)H is used instead of BIH. This is because BI(OH)H can supply more protons during the photocatalytic reaction.

## Experiments

### General procedures

The UV-vis absorption spectra were measured with a JASCO V-565 spectrophotometer.  $^1\text{H}$  NMR spectra were obtained using a JEOL AL400 (400 MHz) system to identify the synthesized

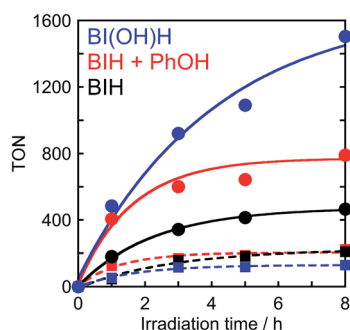


Fig. 10 Photocatalytic formation of formic acid (●) and CO (■) using BI(OH)H (0.1 M, blue), BIH and phenol (0.1 M each, red) or BIH (0.1 M, black): a  $\text{CO}_2$  saturated DMF-TEOA (4 : 1 v/v, 2 mL) solution containing  $\text{Ru}_2\text{-Ru(CO)}$  (0.025 mM), a sacrificial electron donor (0.1 M) and a proton source (0.1 M) was irradiated by  $\lambda_{\text{ex}} > 500$  nm light (LIC2).



compounds in solutions of either  $\text{CDCl}_3$  or acetone- $d_6$ . The tetramethylsilane protons contained in  $\text{CDCl}_3$  and the residual protons of acetone- $d_6$  were used as an internal standard for these measurements. The emission spectra were measured using a JASCO FP-6500 spectrofluorometer. The emission quenching experiments were performed on Ar-saturated solutions containing  $\text{Ru}_2\text{-Ru}(\text{CO})$  and five different concentrations of a sacrificial electron donor. Quenching rate constants  $k_q$  were calculated from linear Stern–Volmer plots for the luminescence of the  $^3\text{MLCT}$  excited state of the photosensitizer units together with knowledge of their lifetimes.

### Photocatalytic reactions

The experimental details of photo-irradiation conditions of the photocatalytic reactions are shown in the ESI.†<sup>6</sup> All of the experiments used 0.1 M concentrations of  $\text{BI}(\text{OH})\text{H}$ ,  $\text{BIH}$ , or  $\text{BNAH}$  in a solvent mixture of DMF and TEOA (4 : 1 v/v). The solutions were purged with  $\text{CO}_2$  for 20 min before irradiation.

The concentrations of CO and  $\text{H}_2$  were analyzed by a GC-TCD (GL science GC323). Formic acid was analyzed using a capillary electrophoresis system (Otsuka Electronics Co. CAPI-3300I). To quantify the amount of formic acid, the photocatalytic reaction solution was pretreated by diluting the solution 10 times with  $\text{H}_2\text{O}$ . As DMF is hydrolyzed to formic acid in the presence of a base,<sup>20</sup> a nonirradiated photocatalytic reaction solution of saturated  $\text{CO}_2$ , which suppresses the hydrolysis of DMF by acting as an acid, was employed as a reference. The reference solution was also measured before and after the quantification of formic acid, and its value was subtracted from the quantified formic acid. It should be emphasized that substantially smaller amounts of formic acid were produced by the hydrolysis of DMF in comparison with the amounts of formic acid produced by the photocatalytic reduction of  $\text{CO}_2$ . This is probably due to the fact that  $\text{CO}_2$  works as an acid. For example, in the photocatalytic reaction that utilizes  $\text{BI}(\text{OH})\text{H}$  under LIC2 (Fig. 2, Table 1), 138  $\mu\text{mol}$  of formic acid was produced by the photocatalytic reduction of  $\text{CO}_2$  after a 20 h irradiation period. In contrast, only 2.0  $\mu\text{mol}$  of formic acid was produced in the reference solution.

The HPLC analyses of  $\text{BI}(\text{OH})\text{H}$  and  $\text{BI}(\text{O}^-)^+$  were accomplished using a JASCO 880-PU pump with a Develosil ODS-UG-5 column (250  $\times$  4.6 mm), a JASCO 880-51 degasser, and a JASCO UV-2070 detector. The column temperature was maintained at 30  $^\circ\text{C}$  with a JASCO 860-CO oven. The mobile phase was a 6 : 4 (v/v) mixture of acetonitrile and a  $\text{NaOH-KH}_2\text{PO}_4$  buffer solution (pH 7) with a flow rate of 0.5  $\text{mL min}^{-1}$ . The retention times were 23.8 min ( $\text{BI}(\text{OH})\text{H}$ ) and 6.3 min ( $\text{BI}(\text{O}^-)^+$ ).

### Labeling experiments using $^{13}\text{CO}_2$

The  $^{13}\text{CO}_2$  experiment was performed in a DMF- $d_7$ -TEOA solution containing  $\text{Ru}_2\text{-Ru}(\text{CO})$  (0.5 mM) and  $\text{BI}(\text{OH})\text{H}$  (0.1 M). The tube was deaerated using the freeze–pump–thaw method before  $^{13}\text{CO}_2$  (569 mmHg) was introduced into the solution.  $^{13}\text{C}\{^1\text{H}\}$ ,  $^{13}\text{C}$ , and  $^1\text{H}$  NMR spectra were measured with a JEOL AL300 (75 MHz for  $^{13}\text{C}$  NMR and 300 MHz for  $^1\text{H}$  NMR) before and after 13.5 h of irradiation using light with a wavelength of more

than 420 nm obtained using a 500 W xenon lamp with a cut-off filter. The residual carbon and proton of DMF- $d_7$  was used as an internal standard for these measurements.

### Time-resolved UV-vis absorption spectroscopy

Second-harmonic-generation light at 532 nm produced with a Spectra-Physics Quanta-Ray LAB-150-10 pulsed Nd:YAG laser was used for excitation (10 ns FWHM). An Ushio 300 W Xe arc lamp was operated in a pulse-enhanced mode (500  $\mu\text{s}$  duration) using an XC-300 power supply and a YXP-300 light pulsar (Eagle Shoji) as a monitoring light source. The monitoring light beam was passed through the quartz cuvette (10  $\times$  10  $\times$  40 mm) that contained a sample and was directed into an R926 photo-multiplier tube (Hamamatsu Photonics) on a Jobin-Yvon HR-320 monochromator. Time profiles of the monitoring light intensity were stored using a LeCroy WaveRunner 640zi oscilloscope (4 GHz bandwidth). Transient spectra were obtained with an Andor Technology iStar H320T-18F-03 (690 channels; minimum gate width: 5 ns) ICCD detector head mounted on the HR-320 monochromator. A DMF-TEOA (5 : 1 v/v) solution that contained  $\text{Ru}$  (0.3 mM), and  $\text{BI}(\text{OH})\text{H}$  or  $\text{BIH}$  (0.1 M) was degassed by freeze–pump–thaw method prior to the laser flash photolysis.

### Quantum yield measurements of the one-electron reduction of Ru

The quantum yield measurements were performed in a quartz cubic cell (light pass length: 1 cm) consisting of  $\text{Ru}$  (0.1 mM) and a sacrificial electron donor (0.1 M) in a DMF-TEOA (5 : 1 v/v, 4 mL) solution. After purging with Ar for 20 min, the solution was irradiated using a 500 W xenon lamp with a 480 nm (FWHM = 10 nm) band pass filter (Asahi Spectra Co.) and a 5 cm long  $\text{CuSO}_4$  solution (250  $\text{g L}^{-1}$ ) filter. The UV-vis absorption spectral changes during irradiation were measured with a Photal MCPD-2000 spectrophotometer. During irradiation, the temperatures of the solutions were maintained at 25  $^\circ\text{C}$  using an IWAKI constant temperature system CTS-134A. The incident light intensity was determined using a  $\text{K}_3\text{Fe}(\text{C}_2\text{O}_4)_3$  actinometer and the number of absorbed photons were calculated on the basis of the absorbance changes at an irradiation wavelength of 480 nm. The amounts of produced  $\text{Ru}^-$  were calculated using the molar absorptivity of  $\text{Ru}^-$ , which was obtained by the electrochemical reduction of  $\text{Ru}$  in an acetonitrile solution containing  $\text{Et}_4\text{NBF}_4$  as an electrolyte.<sup>7</sup>

### Materials

DMF was dried over molecular sieves 4A and distilled under reduced pressure (10–20 mm Hg). TEOA was also distilled under reduced pressure (<1 mm Hg). Both solvents were kept under Ar before use. All other reagents were of reagent-grade quality and used without further purification.  $\text{Ru}_2\text{-Ru}(\text{CO})$ ,<sup>6</sup>  $\text{BI}(\text{OH})\text{H}$ ,<sup>9,12</sup>  $\text{BI}(\text{O}^-)^+$ ,<sup>21</sup> and  $\text{BIH}$ <sup>9,12</sup> were prepared according to the reported methods.

## Conclusion

We found that  $\text{BI}(\text{OH})\text{H}$  is a suitable sacrificial electron donor for the photochemical reduction of  $\text{CO}_2$  to formic acid by the



utilization of  $\text{Ru}_2\text{-Ru(CO)}$  as the photocatalyst. The efficiency, durability, and rate of the photocatalytic reaction using  $\text{Ru}_2\text{-Ru(CO)}$  were all significantly increased when  $\text{BI(OH)H}$  was employed as a sacrificial reductant ( $\Phi_{\text{HCOOH}} = 0.46$ ,  $\text{TON}_{\text{HCOOH}} = 2766$ ,  $\text{TOF}_{\text{HCOOH}} = 44.9 \text{ min}^{-1}$ ) relative to  $\text{BIH}$  or  $\text{BNAH}$ . The electron balance and the material balance of the photocatalysis was also clarified, where one molecule of  $\text{BI(OH)H}$  donates two electrons and two protons to one molecule of  $\text{CO}_2$  to produce one molecule each of  $\text{BI(O}^-\text{)}^+$  and formic acid.

## References

- 1 S. Enthaler, *ChemSusChem*, 2008, **1**, 801–804.
- 2 F. Joó, *ChemSusChem*, 2008, **1**, 805–808.
- 3 R. Tanaka, M. Yamashita and K. Nozaki, *J. Am. Chem. Soc.*, 2009, **131**, 14168–14169.
- 4 R. Langer, Y. Diskin-Posner, G. Leitus, L. J. Shimon, Y. Ben-David and D. Milstein, *Angew. Chem., Int. Ed.*, 2011, **50**, 9948–9952.
- 5 J. F. Hull, Y. Himeda, W.-H. Wang, B. Hashiguchi, R. Periana, D. J. Szalda, J. T. Muckerman and E. Fujita, *Nat. Chem.*, 2012, **4**, 383–388.
- 6 Y. Tamaki, T. Morimoto, K. Koike and O. Ishitani, *Proc. Natl. Acad. Sci. U. S. A.*, 2012, **109**, 15673–15678.
- 7 Y. Tamaki, K. Watanabe, K. Koike, H. Inoue, T. Morimoto and O. Ishitani, *Faraday Discuss.*, 2012, **155**, 115–127.
- 8 Y. Tamaki, K. Koike, T. Morimoto and O. Ishitani, *J. Catal.*, 2013, **304**, 22–28.
- 9 E. Hasegawa, T. Seida, N. Chiba, T. Takahashi and H. Ikeda, *J. Org. Chem.*, 2005, **70**, 9632–9635.
- 10 E. Hasegawa, S. Takizawa, T. Seida, A. Yamaguchi, N. Yamaguchi, N. Chiba, T. Takahashi, H. Ikeda and K. Akiyama, *Tetrahedron*, 2006, **62**, 6581–6588.
- 11 E. Hasegawa, H. Hirose, K. Sasaki, S. Takizawa, T. Seida and N. Chiba, *Heterocycles*, 2009, **77**, 1147–1161.
- 12 X.-Q. Zhu, M.-T. Zhang, A. Yu, C.-H. Wang and J.-P. Cheng, *J. Am. Chem. Soc.*, 2008, **130**, 2501–2516.
- 13 Deprotonation of the hydroxy group of  $\text{BI(OH)H}$  should not proceed in the  $\text{DMF-TEOA}$  (4 : 1 v/v) solution because the  $\pi\text{-}\pi^*$  absorption band of  $\text{BI(OH)H}$  observed at  $\lambda_{\text{max}} = 275 \text{ nm}$  did not change at all between in the presence and absence of  $\text{TEOA}$  (Fig. S1†).
- 14 M. Patz, Y. Kuwahara, T. Suenobu and S. Fukuzumi, *Chem. Lett.*, 1997, 567–568.
- 15 M. J. Berr, P. Wagner, S. Fischbach, A. Vaneski, J. Schneider, A. S. Susa, A. L. Rogach, F. Jäckel and J. Feldmann, *Appl. Phys. Lett.*, 2012, **100**, 223903.
- 16 C. Costentin, S. Drouet, M. Robert and J.-M. Savéant, *Science*, 2012, **338**, 90–94.
- 17 J. M. Smieja, M. D. Sampson, K. A. Grice, E. E. Benson, J. D. Froehlich and C. P. Kubiak, *Inorg. Chem.*, 2013, **52**, 2484–2491.
- 18 J. R. Pugh, M. R. M. Bruce, B. P. Sullivan and T. J. Meyer, *Inorg. Chem.*, 1991, **30**, 86–91.
- 19 H. Ishida, K. Tanaka and T. Tanaka, *Organometallics*, 1987, **6**, 181–186.
- 20 A. Paul, D. Connolly, M. Schulz, M. T. Pryce and J. G. Vos, *Inorg. Chem.*, 2012, **51**, 1977–1979.
- 21 F. Montgrain, S. M. Ramos and J. D. Wuest, *J. Org. Chem.*, 1988, **53**, 1489–1492.

