

Cite this: *Energy Environ. Sci.*,  
2018, 11, 850

## Tuning mobility and stability of lithium ion conductors based on lattice dynamics†

Sokseih Mui,<sup>a</sup> John C. Bachman,<sup>b</sup> Livia Giordano,<sup>c</sup> Hao-Hsun Chang,<sup>d</sup>  
Douglas L. Abernathy,<sup>e</sup> Dipanshu Bansal,<sup>e</sup> Olivier Delaire,<sup>ef</sup> Satoshi Hori,<sup>g</sup>  
Ryoji Kanno,<sup>g</sup> Filippo Maglia,<sup>h</sup> Saskia Lupart,<sup>h</sup> Peter Lamp<sup>h</sup> and  
Yang Shao-Horn<sup>id</sup>\*<sup>abd</sup>

Lithium ion conductivity in many structural families can be tuned by many orders of magnitude, with some rivaling that of liquid electrolytes at room temperature. Unfortunately, fast lithium conductors exhibit poor stability against lithium battery electrodes. In this article, we report a fundamentally new approach to alter ion mobility and stability against oxidation of lithium ion conductors using lattice dynamics. By combining inelastic neutron scattering measurements with density functional theory, fast lithium conductors were shown to have low lithium vibration frequency or low center of lithium phonon density of states. On the other hand, lowering anion phonon densities of states reduces the stability against electrochemical oxidation. Olivines with low lithium band centers but high anion band centers are promising lithium ion conductors with high ion conductivity and stability. Such findings highlight new strategies in controlling lattice dynamics to discover new lithium ion conductors with enhanced conductivity and stability.

Received 27th November 2017,  
Accepted 20th February 2018

DOI: 10.1039/c7ee03364h

rsc.li/ees

### Broader context

Replacing organic liquid electrolytes with solid lithium ion conductors in Li-ion batteries can boost the energy density and also increase battery safety. Current research and development of solid-state lithium ion batteries has been catalyzed by recent breakthroughs in solid lithium ion conductors that have ion conductivities rivaling those of conventional organic liquid electrolytes. However, known fast solid lithium ion conductors are not stable against lithium ion battery electrodes. Of significance, no fast lithium ion conductor known to date is stable against positive electrode materials in lithium ion batteries. Therefore, it is of great importance to design new lithium ion conductors having not only high Li conductivity but also being stable during battery operation. Increasing ion mobility and stability of lithium solid conductors is not straightforward and progress in the past decades has been achieved primarily by trial and error. Structural and chemical tuning *via* isovalent or aliovalent substitution of cation and/or anion in given structural families has led to steady increase in the lithium ion conductivity, and recent discovery of superionic lithium ion conductors. In this article, we report correlations between lattice dynamics and ion mobility or stability against electrochemical oxidation, and highlight opportunities to search for fast, stable lithium ion conductors based on low lithium band center but high anion band center. With rapid advances in the computational capability, we envision these descriptors to be used in high-throughput studies to screen not only lithium ion conductors but also other technologically relevant ion conductors such as oxygen or sodium ion conductors.


<sup>a</sup> Department of Materials Science and Engineering, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139, USA<sup>b</sup> Department of Mechanical Engineering, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139, USA<sup>c</sup> Dipartimento di Scienza dei Materiali, Università di Milano-Bicocca, Milano 20125, Italy<sup>d</sup> Research Laboratory of Electronics, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139, USA<sup>e</sup> Materials Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA<sup>f</sup> Mechanical Engineering and Materials Science, Duke University, Durham, NC 27708, USA<sup>g</sup> Department of Chemical Science and Engineering, School of Materials and Chemical Technology, Interdisciplinary Graduate School of Science and Engineering, Tokyo Institute of Technology, 4259 Nagatsuta, Midori, Yokohama 226-8502, Japan<sup>h</sup> Research Battery Technology, BMW Group, Munich 80788, Germany

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c7ee03364h

## Introduction

Replacing organic liquid electrolytes<sup>1,2</sup> with solid lithium ion conductors in lithium ion batteries enables the use of the metallic lithium to markedly boost the energy density<sup>3,4</sup> and also increases battery safety.<sup>5</sup> Current research and development of solid-state lithium ion batteries has been catalyzed by recent breakthroughs in solid lithium ion conductors that have ion conductivities<sup>6–9</sup> rivaling that of conventional organic liquid electrolytes.<sup>1</sup> Although a number of structural families such as lithium superionic conductors (LISICON),<sup>10,11</sup> garnets,<sup>12</sup> NASICON-like (sodium superionic conductor),<sup>13</sup> and perovskites<sup>14</sup> have ion conductivities approaching that of liquid electrolytes, an increasing number of experimental<sup>15</sup> and computational<sup>16,17</sup>



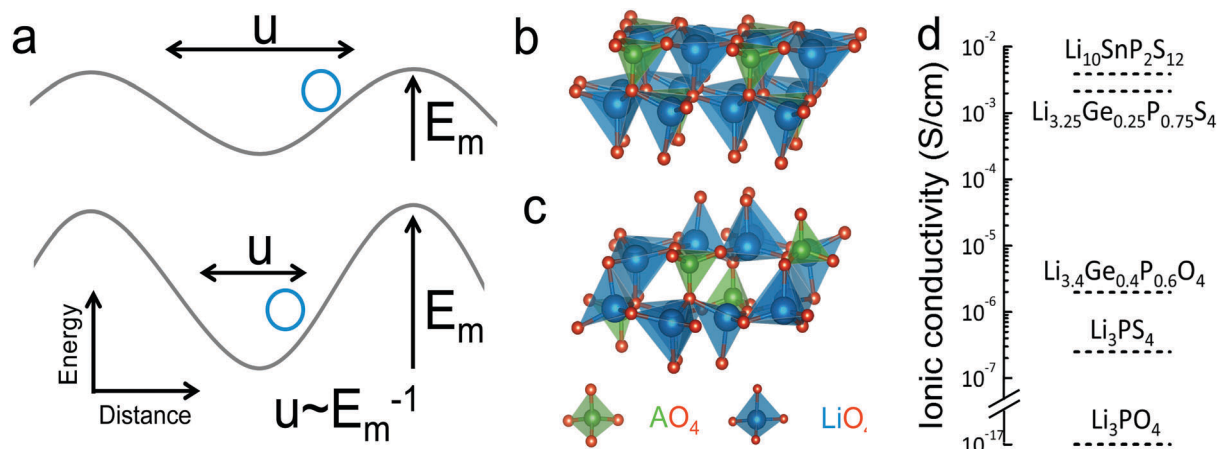

**Fig. 1** (a) Schematic of the energy landscape of lithium ions in lithium ion conductors. The potential energy as a function of the migration pathway distance, where the minima correspond to the equilibrium positions while the maxima correspond to the bottleneck or transition state, where lithium ions come to be the closest to anions (b) low-temperature (LT) structure of LISICON (space group  $Pmn2_1$ ). (c) High-temperature (HT) structure of LISICON (space group  $Pnma$ ), where lithium and phosphorus occupy the tetrahedral interstices, leaving all the octahedral sites empty, within the distorted hexagonal oxygen sublattice. All the  $\text{LiO}_4$  tetrahedra point in the same direction in LT- $\text{Li}_3\text{PO}_4$ <sup>24</sup> while  $\text{LiO}_4$  tetrahedra of HT- $\text{Li}_3\text{PO}_4$ <sup>24</sup> point in the two opposite directions. (d) Room-temperature ionic conductivity of some representative LISICON included in this study ( $\text{Li}_3\text{PO}_4$ - $Pnma$ ,<sup>24</sup>  $\text{Li}_3\text{PS}_4$ - $Pmn2_1$ ,<sup>20</sup>  $\text{Li}_{3.4}\text{Ge}_{0.4}\text{P}_{0.6}\text{O}_4$ - $Pnma$ ,<sup>10</sup>  $\text{Li}_{3.25}\text{Ge}_{0.25}\text{P}_{0.75}\text{S}_4$ - $Pnma$ <sup>18</sup> and  $\text{Li}_{10}\text{SnP}_2\text{S}_{12}$ - $P6_3/nmc$ <sup>8</sup>).

studies show that fast solid lithium ion conductors are not stable against lithium ion battery electrodes. Of significance, no known fast solid lithium conductors is stable against lithium ion positive electrode materials,<sup>16</sup> highlighting critical needs to search for new lithium solid conductors with high lithium ion conductivity and stability.

Increasing ion mobility and stability of lithium solid conductors is not straightforward and progress in the past decades has been achieved primarily by trial and error. Structural and chemical tuning *via* isovalent or aliovalent substitution of cation<sup>10,11</sup> and/or anion<sup>18–20</sup> in given structural families has led to steady increase in the lithium ion conductivity, and recent discovery of superionic lithium ion conductors.<sup>6–9</sup> Recently a number of structure-based ion conductivity descriptors have been proposed to aid and accelerate the design of new superionic conductors including the volume of the unit cell<sup>10,13,21</sup> the volume of lithium diffusion pathway,<sup>22</sup> the anion in the structure,<sup>21</sup> and the structure of the anion sublattices.<sup>23</sup> For example, increasing lattice volume in the LISICON,<sup>10</sup> NASICON-like,<sup>13</sup> or perovskite<sup>14,21</sup> structure can enhance ion conductivity and reduce activation energy.<sup>21</sup> In addition, changing the anions by moving down in the periodic table (*e.g.*  $\text{Li}_{10}\text{GeP}_2\text{X}_{12}$ , ( $\text{X} = \text{O}, \text{S}$  and  $\text{Se}$ )<sup>17</sup> or  $\text{Li}_3\text{PX}_4$  ( $\text{X} = \text{O}$ <sup>24</sup> and  $\text{S}$ <sup>20</sup>)) and/or arranging anions in a body centered cubic lattice<sup>23</sup> can increase lithium ion conductivity by reducing activation energy. Unfortunately, most of these descriptors have limited predictive power when applied across different structure families and chemistry of lithium ion conductors.<sup>21</sup> Direct computation of Li-ion conductivity using *ab initio* molecular dynamics (AIMD) has also been pursued as a way to discover/design new materials with higher ionic conductivity.<sup>25,26</sup> However, this method is computationally very demanding not to mention various practical limitations such as the need to extrapolate ionic conductivity from high temperature to room temperature. Moreover, no design principle is established

for the stability of lithium solid conductors. Limited predictive power of reported conductivity descriptors and the lack of stability descriptor hampers the search for new lithium-ion conductors with enhanced conductivity and stability in order to meet all the requirements of solid-state lithium-ion batteries. In this article, we report a new approach to design lithium ion mobility and stability of lithium ion conductors using their lattice dynamical properties. We relate lithium ion mobility to lattice dynamics based on the following hypothesis: small energetic barrier for lithium ion migration (enthalpy of migration) is associated with large displacement amplitude from their equilibrium sites (Fig. 1a), rendering greater probability for lithium ions to explore multiple energy minima. Large excursions of mobile ions away from the equilibrium position are enabled in the soft atomic potential and also are associated with low phonon frequencies considering the Einstein model, where the amplitude of thermal displacement  $u$  of the ion is inversely proportional to the square of the frequency  $\omega_E$  using:<sup>27</sup>  $\langle |u|^2 \rangle = 3k_B T / m\omega_E^2$ , having  $k_B$ ,  $T$  and  $m$  denote the Boltzmann constant, temperature and the mass of the mobile species, respectively. In contrast, with a high migration barrier, the mobile species oscillate close to their equilibrium position with small thermal displacement amplitude and high frequency, and have low probability of hopping to adjacent sites. The hypothesis is supported by the following observations. The self-diffusion coefficient and the activation energy of metal atoms in body center cubic metal strongly correlate with the frequency of the longitudinal acoustic mode along the  $\langle 111 \rangle$  direction (at reduced wavevector  $q = 2/3$ ), being higher with lower frequency.<sup>28</sup> Second, the computed migration enthalpy of oxygen diffusion *via* interstitially in rare-earth Ruddlesden–Popper phases shows strong positive correlation with reduced (more negative) force constant of the soft mode associated with the rotation of  $\text{AO}_6$  octahedra ( $\text{A} = \text{rare-earth metal ions}$ ).<sup>29</sup> Third, Wakamura has shown that the activation



energy in  $\text{Ag}^+$ ,  $\text{Na}^+$ ,  $\text{Cu}^+$  and  $\text{F}^-$  superionic conductors decreases with decreasing frequency of low-energy optical mode<sup>30</sup> supporting the idea that low phonon frequency can be associated with high probability of ions hopping to the neighboring sites.<sup>21</sup>

We elected to study a series of lithium ion conductors in the LISICON family derived from  $\text{Li}_3\text{PO}_4$ , to test the hypothesis that their lattice dynamics can greatly influence lithium ion mobility and stability. Lithium ion conductivity can be increased by up to 15 orders of magnitude<sup>10,11,18,20,21</sup> via cation and anion substitutions in this structural family relative to  $\text{Li}_3\text{PO}_4$  (Fig. 1d). We also included Olivine structure which has the same (distorted) hexagonal close packed of anion sublattice as the LISICON compounds but differ in occupancy of Lithium ions which are located in octahedral sites as opposed to tetrahedral sites in LISICON structure. Although substitution (doping) and defects may alter migration pathway and mechanism and the activation energy, we have selected lithium ion conduction in LISICON and Olivine, having similar one-dimensional channels of Li ions within hexagonal anion sublattice. Previous work has shown that in Olivine, these one-dimensional channels serve as the dominant pathway for lithium migration and govern ion conduction in this structure.<sup>50</sup> In Lisicon, although the diffusion pathway is three-dimensional,<sup>31</sup> previous study has shown that the enthalpies of vacancies migration along each crystallographic direction are very similar and on the order of 0.7 eV in both  $\gamma\text{-Li}_3\text{PO}_4$  and  $\beta\text{-Li}_3\text{PO}_4$ .<sup>32</sup> It should be mentioned that depending on the concentration of mobile specie, the dominant diffusion mechanism might be interstitial instead of vacancy diffusion considered here. Nevertheless, we believe that the trends that we propose here remain valid as long as one considers the same mechanism with similar diffusion pathway regardless of the compound chemistries and structures. Isovalent substitution of oxygen by sulfur anion can enhance the ionic conductivity by six orders of magnitude, having reduced activation energy from 1.3<sup>24</sup> to 0.52 eV,<sup>20</sup> and additional four orders of magnitude by aliovalent substitution of phosphorus by germanium, with decreasing activation energy from 0.52 to 0.21 eV.<sup>18</sup> In this work, we systematically study the lattice dynamics of LISICONS derived from  $\text{Li}_3\text{PO}_4$  by measuring the phonon density of states (DOS) of 17 compounds and one olivine compound as well as computing the phonon DOS of more than 20 compounds which are isostructural to LISICON and 6 olivines. The reader is referred to the Table S1 in (ESI†) for a complete list of compounds included in this study. From these data, combined with the measured activation energy, computed enthalpy of lithium ion migration of LISICONS and computed potential for electrochemical oxidation, the descriptors for lithium ion mobility and stability for oxidation were proposed.

## Experimental and computation methods

All phonon DOS measurements were made at the Wide-angular range chopper spectrometer (ARCS) at the Spallation Neutron

Source at Oak Ridge National Labs. Approximately 5 g of the samples were packed into aluminum canisters, which were sealed with a vanadium ring, unless spectra at elevated temperatures were measured where a qualitative (aluminum on aluminum) seal was used. All samples were sealed under argon. Temperatures were varied from 10 K to 600 K for select samples. Unless otherwise noted, the samples were measured at 100 K. The incident neutron energies were varied between 60, 100, and 200 meV. The resulting data were analyzed using the Mantid DGS Reduction package. For oxides, the background fraction was set as 1, the fraction of the total scattering to subtract as a constant background was 0.0–0.25 unless otherwise noted, the cutoff for the elastic peak removal was set as 10 meV, 3 bins after the cutoff were averaged to get the value of the density of states near the cutoff, the estimate of the Debye cutoff and the limit on the energy range were set depending on the calculated phonon density of states and where the last feature in the experimental density of states was noted (these parameters were used to remove any high energy background), and the range in wave vector that was used was from 7–12  $\text{\AA}^{-1}$ . For sulfides, the parameters were the same except the range of wave vectors used was from 4–9  $\text{\AA}^{-1}$ .

For computations, we used density functional theory based on the Perdew–Burke–Ernzerhof (PBE) generalized gradient approximation<sup>33</sup> as implemented in the VASP package.<sup>34</sup> The core electrons were treated within the Projector Augmented Wave (PAW) method.<sup>35</sup> Migration barriers for a lithium ion hopping were calculated using the climbing-image nudged elastic band method<sup>36</sup> in a  $2 \times 2 \times 1$  supercell for LISICON (space group  $Pnma$ ) while for the LISICON (space group  $Pnm2_1$ ), a  $2 \times 2 \times 2$  supercell was employed. A  $2 \times 2 \times 2$   $k$ -point grid was used and the cutoff of the kinetic energy was set to the default values as set in the pseudopotential files. For phonon calculations, the same supercells were used with finer  $k$ -point grid ( $3 \times 3 \times 3$ ) and a higher energy cutoff (520 eV) in order to obtain more accurate values of the force. We have also used a higher cut-off energy of 700 eV for phonon DOS calculations but haven't found any significant change (Fig. S1, ESI†) indicating that phonon DOS calculations are already well converged at 520 eV of cut-off energy. We have also tested LDA functional for phonon DOS calculations and found that the main effect of is to shift all the modes especially the high-energy feature in the DOS to higher frequencies resulting in an upward shift of band center (Fig. S1, ESI†) in agreement with previous study.<sup>37</sup> However, the magnitude of the shift is small and fairly constant across different chemistries and crystal structures suggesting that LDA functional will result in a rigid shift to slightly higher energy but will not affect the trend. Finite displacement method was used for phonon calculations and the total as well as the atom-projected DOS were extracted using the phonopy package.<sup>38</sup>

To quantify the average vibrational frequency of a given material, we defined the 'phonon band center' which is the phonon frequency weighted by the DOS. Mathematically, it is written as:

$$\omega_{\text{av}} \equiv \frac{\int \omega \times \text{DOS}(\omega) d\omega}{\int \text{DOS}(\omega) d\omega}$$

If we replace  $\text{DOS}(\omega)$  in this expression by the total phonon DOS, we obtain what we called 'total phonon band center'. Similarly, if we replace  $\text{DOS}(\omega)$  by one of the atom-projected





**Fig. 2** Measured phonon DOS and computed total and lithium-projected phonon DOS. Experimental phonon DOS collected at 100 K are shown on top while computed phonon DOS at 0 K on the bottom as well as the computed lithium-projected DOS (shaded). (a)  $\text{Li}_3\text{PO}_4$  (*Pnma*) (b)  $\text{Li}_3\text{PS}_4$  (*Pnm2\_1*) (c)  $\text{Li}_{3.4}\text{Ge}_{0.4}\text{P}_{0.6}\text{O}_4$  (*Pnma*) and (d)  $\text{Li}_{3.25}\text{Ge}_{0.25}\text{P}_{0.75}\text{S}_4$  (*Pnma*). The measured phonon DOS data were obtained after background correction, optimizing lower and higher energy cut-off and details can be found in Fig. S4 (ESI<sup>†</sup>). The computed DOS were weighted by neutron scattering cross section of the different elements that make up the structures. The details of this procedure can be found in previous work.<sup>67</sup>



**Fig. 3** Comparison between computed and measured total phonon band centers of 7 stoichiometric LISICONs, one substituted LISICON  $\text{Li}_{3.25}\text{Ge}_{0.25}\text{P}_{0.75}\text{S}_4$  (chemically similar to  $\text{Li}_{10}\text{GeP}_2\text{S}_{12}$ ) and  $\text{Li}_4\text{GeO}_4$  (*Cmcm*) at 100 K. The measured phonon band centers of LISICON  $\text{Li}_{10}\text{SnP}_2\text{S}_{12}$  (*P4\_2/nmc*) and  $\text{Li}_{3.4}\text{Ge}_{0.4}\text{P}_{0.6}\text{S}_4$  (*P4\_2/nmc*) were not included as computed phonon band centers could not be obtained due to the presence of imaginary modes in the phonon DOS of  $\text{Li}_{10}\text{SnP}_2\text{S}_{12}$  and absence of refined atomic structure details of  $\text{Li}_{3.4}\text{Ge}_{0.4}\text{P}_{0.6}\text{S}_4$ . The computed band centers were calculated using the neutron-weighted computed DOS. The computed values are systematically lower than the experimental values, as expected from the use of the GGA functional in the calculations.

DOS for instance Li-projected DOS, we obtain the ‘Lithium phonon band center’ which can also be viewed as the centroid of the Li-projected phonon DOS. The stability windows were computed following the method proposed by Richard *et al.*<sup>16</sup> using the data from Materials project database<sup>39</sup> and Pymatgen software package.<sup>40</sup> The stability window was computed by constructing the grand potential phase diagram and varying the chemical potential of Li until the grand potential of the electrolytes were above the convex hull.<sup>41</sup> Measured phonon DOS of 17 LISICON and LISICON-like compounds can be found in Fig. 2–4 and Fig. S2 (ESI<sup>†</sup>), computed phonon DOS of some of these compounds and additional LISICONs available in the ICSD can be found in Fig. 2 and Fig. S3 (ESI<sup>†</sup>). The measured phonon band centers (100 K) was in excellent agreement with computed values for 7 stoichiometric LISICONs, one substituted LISICON  $\text{Li}_{3.25}\text{Ge}_{0.25}\text{P}_{0.75}\text{S}_4$  (chemically similar to  $\text{Li}_{10}\text{GeP}_2\text{S}_{12}$ ) and  $\text{Li}_4\text{GeO}_4$  (*Cmcm*), as shown in Fig. 3. A systematic red shift of the computed total band center with respect to the measured total band center can be partially attributed to a well-known issue of over-estimated lattice parameters associated with GGA functional (PBE)<sup>33</sup> relative to measured values, giving rise to softening of high-energy modes and thus the total phonon band center.

## Results and discussions


### Influence of chemical substitution and temperature on phonon DOS of lithium conductors

Cation and anion substitutions in the  $\text{Li}_3\text{PO}_4$  structural family were shown to induce systematic changes by examining measured

phonon DOS of 17 LISICON-like compounds and computed phonon DOS of 20 LISICONs. The measured and computed phonon DOS of  $\text{Li}_3\text{PO}_4$  (*Pnma*),  $\text{Li}_3\text{PS}_4$  (*Pnm2\_1*),  $\text{Li}_{3.4}\text{Ge}_{0.4}\text{P}_{0.6}\text{O}_4$  (*Pnma*) and  $\text{Li}_{3.25}\text{Ge}_{0.25}\text{P}_{0.75}\text{S}_4$  (*Pnma*) are shown as example in Fig. 2a–d, and those of the other LISICON-like compounds can be found in Fig. 4 and Fig. S2, S3 of the (ESI<sup>†</sup>). The phonon DOS measured at 100 K (the upper spectrum of each panel in Fig. 2) is in quantitative agreement with the DOS computed from DFT at 0 K (the lower spectrum). Substitution of oxygen by sulfur led to significant softening of phonon modes.  $\text{Li}_3\text{PO}_4$  (*Pnma*) in Fig. 2a and  $\text{Li}_{3.4}\text{Ge}_{0.4}\text{P}_{0.6}\text{O}_4$  (*Pnma*) in Fig. 2c were found to have higher energy phonon DOS than  $\text{Li}_3\text{PS}_4$  (*Pnm2\_1*) in Fig. 2b and  $\text{Li}_{3.25}\text{Ge}_{0.25}\text{P}_{0.75}\text{S}_4$  (*Pnma*) in Fig. 2d. Similar lattice softening were found for other sulfides relative to oxides in Fig. S2 and S3 (ESI<sup>†</sup>). Contribution from lithium ion vibrations (lithium-projected phonon DOS) in the measured total phonon DOS was identified by comparison with the computed atom-projected DOS, as shown in Fig. 2 and Fig. S3 (ESI<sup>†</sup>). Generally speaking, the computed phonon DOS of LISICONs show that low-energy, mid-energy and high-energy features originate mainly from the vibrations of anion sublattice, lithium sublattice and anion units involving non-mobile, structural cations (Fig. S3, ESI<sup>†</sup>) such as  $\text{PO}_4$ , respectively. Of significance,  $\text{Li}_3\text{PO}_4$  (*Pnma*) was found to have phonon DOS peaks in the range from 40–70 meV, which primarily came from lithium ion vibrations, as shown in Fig. 2a and Fig. S3 (ESI<sup>†</sup>). Substituting oxygen in  $\text{Li}_3\text{PO}_4$  (*Pnma*) by sulfur to form  $\text{Li}_3\text{PS}_4$  (*Pnma* and *Pnm2\_1*) led to a down-shifting (softening) of lithium ion vibrations from 40–70 meV to 40–50 meV (Fig. 2b and Fig. S2, S3, ESI<sup>†</sup>).





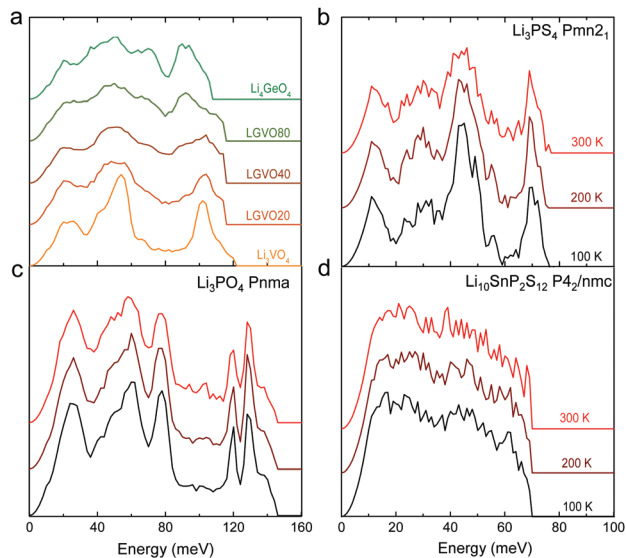

**Fig. 4** Measured phonon DOS as function of aliovalent substitution and temperature. (a) Measured phonon DOS of the series  $\text{Li}_{3+x}\text{Ge}_x\text{V}_{1-x}\text{O}_4$  ( $x = 0, 0.2, 0.4, 0.8$  and  $1$ ) (abbreviated as LGVO20, LGVO40 and LGVO80 for  $x = 0.2, 0.4$  and  $0.8$  respectively) measured at  $100\text{ K}$ . (b) The phonon DOS of  $\text{Li}_3\text{PS}_4$  ( $Pnma$ ) measured at  $100, 200$  and  $300\text{ K}$ , which shows marked broadening at  $\sim 50\text{ meV}$ . (c) The phonon DOS of  $\text{Li}_3\text{PO}_4$  ( $Pnma$ ) measured at  $100, 200$  and  $300\text{ K}$ , which shows little variation with temperature. (d) The phonon DOS of  $\text{Li}_{10}\text{SnP}_2\text{S}_{12}$  that are featureless measured at  $100, 200$  and  $300\text{ K}$ . The measured phonon DOS data were obtained after background correction, optimizing lower and higher energy cut-off and details can be found in Fig. S4 (ESI<sup>†</sup>).

Aliovalent cation substitution induces broadening of features in the phonon DOS, without significant softening. Phonon peaks, including the peak that primarily came from lithium ion vibrations in the range from  $40\text{--}70\text{ meV}$ , was broadened systematically with increasing Ge substitution in  $\text{Li}_{3+x}\text{Ge}_x\text{V}_{1-x}\text{O}_4$ , where  $x = 0, 0.2, 0.4, 0.8$  and  $1$  ( $\text{Li}_3\text{VO}_4$ , LGVO20, LGVO40, LGVO80 and  $\text{Li}_4\text{GeO}_4$ ) in Fig. 4a. Similar broadening of lithium phonon DOS was observed for  $\text{Li}_{3.4}\text{Ge}_{0.4}\text{P}_{0.6}\text{O}_4$  ( $Pnma$ ) and  $\text{Li}_{3.25}\text{Ge}_{0.25}\text{P}_{0.75}\text{S}_4$  ( $Pnma$ ) upon substituting P with Ge in  $\text{Li}_3\text{PO}_4$  ( $Pnma$ ) and  $\text{Li}_3\text{PS}_4$  ( $Pnm2_1$ ), respectively, as shown in Fig. 2. On the other hand, isovalent cation substitution by heavier ions such as replacing P with V in  $\text{Li}_3\text{PO}_4$  (Fig. S5a, ESI<sup>†</sup>) led to minimal downshifting of lithium band center but large downshifting of high-energy phonon modes involving non-mobile, structural cations, to the extent which shared similar energy to lithium phonon DOS in the case of sulfides (Fig. S5b, ESI<sup>†</sup>). Therefore, the broadening of lithium ion vibrations can be attributed to increasing disorder by introducing defects into the LISICON structure<sup>42</sup> such as increasing partial occupancy in the lithium sublattice. This hypothesis is supported by marked broadening of lithium phonon modes observed for  $\text{Li}_3\text{PS}_4$  upon increasing temperature from  $100\text{ K}$  to  $300\text{ K}$  while remaining phonon DOS features of less mobile  $\text{PS}_4$  units in  $\text{Li}_3\text{PS}_4$  showed negligible changes, as shown in Fig. 4b. This broadening can be explained by greater lithium partial occupancy and large displacement amplitudes (anharmonicity)<sup>42</sup> of lithium ions in  $\text{Li}_3\text{PS}_4$  as expected from its low migration barrier ( $\sim 0.5\text{ eV}$ ), in agreement with the concept discussed

in Fig. 1a. Further support came from the observation that no broadening of lithium vibration modes at  $\sim 50\text{ meV}$  was noted for  $\text{Li}_3\text{PO}_4$  (Fig. 4c), since the partial lithium occupancy (or mobile lithium ion concentration) is low ( $\sim 2.05 \times 10^8\text{ cm}^{-3}$  at  $300\text{ K}$  using lithium vacancy formation energy of  $\sim 1.7\text{ eV}$ ),<sup>43</sup> and small displacement amplitudes. Furthermore,  $\text{Li}_{10}\text{SnP}_2\text{S}_{12}$  (isostructural to  $\text{Li}_{10}\text{GeP}_2\text{S}_{12}$ ), with disordered lithium sublattice and liquid-like lithium ion conductivity at room temperature,<sup>8</sup> was found to have phonon DOS so broadened that no peak feature was visible, which did not change upon heating from  $100$  to  $300\text{ K}$ , as shown in Fig. 4d.

### Correlation between Li-band center and enthalpy of migration

Softening of phonon DOS for LISICONs was found to correlate with decreasing measured activation energy for lithium ion conductivity. Increasing temperature has negligible influence on this phonon band center, which is supported by temperature-dependent phonon DOS in Fig. 4b and c, showing no softening of phonon frequencies with increasing temperature. Downshifting the total phonon band center was shown to markedly lower measured activation energy of stoichiometric LISICONs, as shown in Fig. 5a. Replacing oxygen with sulfur from  $\text{Li}_3\text{PO}_4$  ( $Pnm2_1$ ) to  $\text{Li}_3\text{PS}_4$  ( $Pnm2_1$ ) led to the largest downshift of the total phonon band center from  $\sim 70$  to  $\sim 40\text{ meV}$ , which was correlated with reduction of activation energy from  $1.4\text{ eV}$ <sup>24</sup> to  $0.5\text{ eV}$ <sup>20</sup> in Fig. 5a. Measured activation energy of  $\text{Li}_3\text{PO}_4$  ( $Pnma$ ),  $\text{Li}_3\text{VO}_4$  ( $Pnm2_1$ ),  $\text{Li}_{3.4}\text{Ge}_{0.4}\text{P}_{0.6}\text{O}_4$  ( $Pnma$ ) and  $\text{Li}_{3+x}\text{Ge}_x\text{V}_{1-x}\text{O}_4$  ( $x = 0.2, 0.4, 0.6$  and  $1$ ) obtained in this study are in agreement with previous EIS measurements.<sup>10,24,44,45</sup> As the measured activation energy of stoichiometric LISICONs consists of both enthalpy of defect formation and enthalpy of migration, such a correlation for stoichiometric LISICONs does not explicitly imply lowered lithium migration barrier with softening of the total phonon band center. We further show that the measured activation energy for 8 substituted LISICONs with partial lithium occupancy, which corresponds largely to lithium ion migration enthalpy, was decreased with softening of the total phonon band center.  $\text{Li}_{3.4}\text{Ge}_{0.4}\text{P}_{0.6}\text{S}_4$  ( $P6_2/nmc$ ) and  $\text{Li}_{3.25}\text{Ge}_{0.25}\text{P}_{0.75}\text{S}_4$  (chemically similar to  $\text{Li}_{10}\text{GeP}_2\text{S}_{12}$ ),  $\text{Li}_{10}\text{SnP}_2\text{S}_{12}$  ( $P6_2/nmc$ )<sup>8</sup> were found to have the lowest activation energy of  $\sim 0.25\text{ eV}$  comparable to best superionic conductors<sup>6–9</sup> with the lowest measured total band centers of  $\sim 40\text{ meV}$ . Another interesting observation that we can draw from Fig. 5a is the clear separation between stoichiometric and non-stoichiometric compounds which follows two distinct trend lines whose difference is essentially related to the enthalpy of defect formation. It is well-known in perovskites that the enthalpy of migration of oxygen ions decreases with decreasing enthalpy of vacancy formation.<sup>46</sup> Although, in this study, we do not consider the energetic of lithium defect formation energy, in light of the data shown in Fig. 5a, one might hypothesize that the enthalpy of Lithium defect formation might also correlate with phonon band center.

As the total phonon band center can be weighted considerably for the vibrations of non-mobile species such as structural cations and anions, we further sought correlations between the band center of lithium-projected phonon DOS and activation energy.



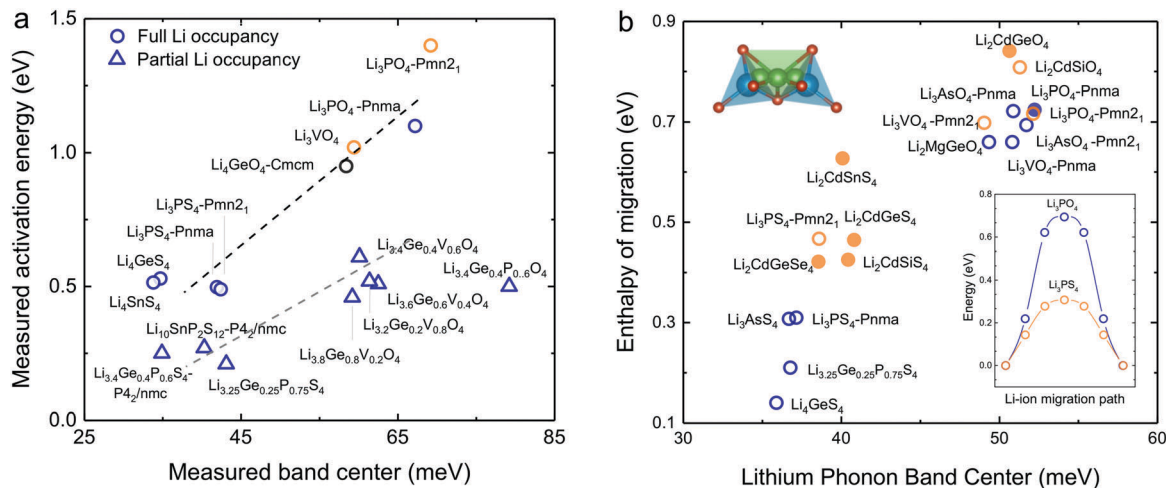


Fig. 5 (a) Comparison between measured activation energy and measured (total) band center of 7 stoichiometric LISICONS and  $\text{Li}_4\text{GeO}_4$  ( $Cmcm$ ), where the activation energy contains contribution from the enthalpy of defect formation and migration enthalpy, and 8 substituted LISICONS with partial occupancy, where the activation energy is essentially the enthalpy of migration. The activation energy were measured using electrical impedance spectroscopy (EIS) (Fig. S6, ESI<sup>†</sup>), and are consistent with prior work  $\text{Li}_3\text{PO}_4$  ( $Pnma$ ),<sup>24</sup>  $\text{Li}_3\text{VO}_4$  ( $Pnnm_2$ ),<sup>44</sup>  $\text{Li}_4\text{GeO}_4$  ( $Cmcm$ ),<sup>45</sup> and  $\text{Li}_{3+x}\text{Ge}_x\text{V}_{1-x}\text{O}_4$  ( $x = 0.2, 0.4, \text{ and } 0.6$ ).<sup>10</sup> Activation energy of  $\text{Li}_3\text{PS}_4$  ( $Pnnm_2$  and  $Pnma$ ),<sup>20</sup>  $\text{Li}_4\text{GeS}_4$ ,<sup>19</sup>  $\text{Li}_4\text{SnS}_4$ ,<sup>68</sup> and  $\text{Li}_{10}\text{SnP}_2\text{S}_{12}$  ( $P4_2/nmc$ )<sup>8</sup> was taken from previous work. The blue and orange colours refer to the HT phase (space group  $Pnma$ ) and the LT phase (space group  $Pnnm_2$ ), respectively. (b) Correlation between computed enthalpy of migration and oxidation potential with computed phonon band center. The computed enthalpy of migration of 15 stoichiometric LISICONS known in the ICSD and 2 computed structures correlated well with the computed lithium band center at 0 K.

In addition, we computed the enthalpy of migration, which would allow us to systematically examine both stoichiometric LISICONS without partial occupancy and substituted LISICONS with partial occupancy. The downshifting of lithium phonon band center or average lithium ion vibration frequency was found to correlate with reduced migration barrier and thus greater lithium mobility, supporting the hypothesis described in Fig. 1a. Lithium ion migration enthalpy, which was defined as the difference between transition state energy and that of the initial/final configuration, was computed using nudge elastic band (NEB) calculations.<sup>36</sup> Identical jump sequence along the diffusion pathway shown in Fig. 5b inset was used to compute the enthalpy of lithium ion migration even though this jump sequence might not be associated with the lowest migration enthalpy. In addition to 7 stoichiometric LISICONS and one substituted LISICONS in Fig. 3, we included 8 others stoichiometric LISICONS in the inorganic crystal structure database (ICSD) in Fig. 5b, which represent all stoichiometric LISICONS (excluding those containing transition metals) and two computed structures ( $\text{Li}_2\text{CdSiS}_4$  and  $\text{Li}_2\text{CdGeSe}_4$ ) to complete the series of  $\text{Li}_2\text{CdXS}_4$  ( $X = \text{Si, Ge and Sn}$ ) and  $\text{Li}_2\text{CdGeY}_4$  ( $Y = \text{O, S and Se}$ ). Decreasing computed lithium band center of 17 stoichiometric LISICONS and one substituted LISICONS  $\text{Li}_{3.25}\text{Ge}_{0.25}\text{P}_{0.75}\text{S}_4$  (chemically similar to  $\text{Li}_{10}\text{GeP}_2\text{S}_{12}$ ) was shown to markedly reduce the lithium ion enthalpy of migration of stoichiometric LISICONS (computed) and  $\text{Li}_{3.25}\text{Ge}_{0.25}\text{P}_{0.75}\text{S}_4$  (measured activation energy) from  $\sim 0.85$  to  $\sim 0.15$  eV, as shown in Fig. 5b. In contrast, the correlation with the computed ligand band center (Fig. S7a, ESI<sup>†</sup>) and total band center (Fig. S7b, ESI<sup>†</sup>) was poor. Similar to the trend of total band centers (Fig. 5a), replacing oxygen with sulfur had the largest influence in downshifting the lithium band center and decreasing enthalpy of lithium ion

migration. The softening from  $\sim 50$  meV for  $\text{Li}_3\text{PO}_4$  ( $Pnma$ ) to  $\sim 37$  meV for  $\text{Li}_3\text{PS}_4$  ( $Pnma$ ) was correlated with a large drop in the migration barrier from  $\sim 0.7$  eV to  $\sim 0.3$  eV. Of significance,  $\text{Li}_{3.25}\text{Ge}_{0.25}\text{P}_{0.75}\text{S}_4$  (chemically similar to  $\text{Li}_{10}\text{GeP}_2\text{S}_{12}$ ) were found to have the lowest measured (Fig. 5a) and computed enthalpy (Fig. 5b) of lithium ion migration of  $\sim 0.2$  eV, which is comparable to that of conventional liquid electrolytes used in lithium ion batteries<sup>1</sup> and fast lithium ion conductors such as  $\text{Li}_7\text{P}_3\text{S}_{11}$ ,<sup>9</sup>  $\text{Li}_{10}\text{GeP}_2\text{S}_{12}$ ,<sup>6</sup> or  $\text{Li}_{9.54}\text{Si}_{1.74}\text{P}_{1.44}\text{S}_{11.7}\text{Cl}_{0.3}$ .<sup>7</sup> The softened or low average lithium vibration frequency and low migration barriers found for fast lithium conductors in this study, which would facilitate more frequent successful hopping of lithium ions also favor concerted hopping<sup>47</sup> of lithium ions as opposed to isolated jumps in conventional ionic conductors. Therefore, computed lithium band center or the average lithium vibration frequency is proposed as one descriptor for lithium ion mobility for LISICONS and other lithium ion conductors.

### Correlation between anion-band center and oxidation potential

Lowering the anion phonon band center was found to greatly reduce the stability of these LISICONS against electrochemical oxidation, as shown in Fig. 6. The oxidation potential was defined as the potential above which LISICONS will be oxidized electrochemically by lithium ion removal from the lattice, which was computed using a thermodynamic approach as reported by Richards *et al.*<sup>16</sup> Replacing oxygen with sulfur in the LISICONS structure had the largest downshift of the anion phonon band center and largest reduction in the oxidation potential. While oxidative stability can be understood in term of electronic structures of the electrolytes which correlate with the thermodynamic driving force to oxidize the materials,<sup>41</sup> the correlation between the oxidation potential and the anion band center



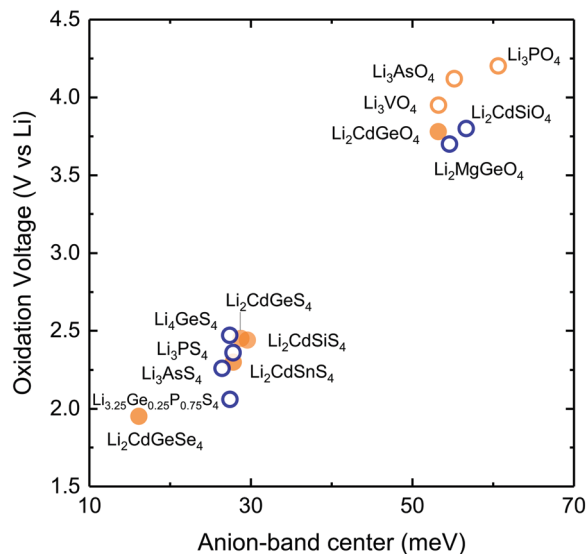


Fig. 6 Correlation between computed stability oxidation potential with the computed anion band center of 13 stoichiometric LISICONS. For each LISICON, the stability window of the most stable phase (lowest formation energy) was computed by constructing the grand potential phase diagram and varying the chemical potential of Li until its grand potential was above the convex hull. The blue and orange colours refer to the HT phase (space group  $Pmna$ ) and the LT phase (space group  $Pmn2_1$ ), respectively. Measured activation energy of substituted LISICON  $\text{Li}_{3.25}\text{Ge}_{0.25}\text{P}_{0.75}\text{S}_4$  (chemically similar to  $\text{Li}_{10}\text{GeP}_2\text{S}_{12}$ ) and its computed lithium band center and computed oxidation potential in this study are included for comparison.

shown in Fig. 6 might be kinetics in origin as lowering anion band center will make anion sublattice more mobile, thus lowering the kinetic barrier for the (decomposition) reactions. Moreover, the stability of a compound can be governed by kinetic properties (migration barriers) and thermodynamics properties. Well-known principles of understanding/controlling kinetics based on thermodynamics include the Evans–Polanyi principle or linear free energy relation, which relates the activation energy of chemical reactions (kinetics property) to the enthalpy of reactions (thermodynamics property). We believe that the correlation between the oxidation potential and anion band center is another instance of this type of ‘kinetic–thermodynamic’ relationships, which is thought in the following ways: as Li-band centers correlate with the enthalpy of lithium migration we argue that lowering the anion-band centers correlate with smaller enthalpy of anion migration (kinetic property), which promotes the kinetics of reactions. This kinetics property, by the Evans–Polanyi principle, correlates with oxidative stability (thermodynamic property) as measured by the oxidation potential. We recognize that more studies are needed to substantiate this idea. Nevertheless, we believe that this work will spur interests from the community to further explore this concept and its potential implications. Softening of the anion band center from  $\text{Li}_3\text{PO}_4$  ( $Pnm2_1$ ) to  $\text{Li}_3\text{PS}_4$  ( $Pmna$ ) by  $\sim 30$  meV is accompanied with reduction of the oxidation potential from  $\sim 4$  to  $\sim 2.5$  V vs. lithium. The computed oxidation potential of  $\text{Li}_3\text{PO}_4$  ( $Pnm2_1$ ) and  $\text{Li}_3\text{PS}_4$  ( $Pmna$ ) are in agreement with previous computation.<sup>16,17</sup> The computed oxidation potential of  $\text{Li}_{3.25}\text{Ge}_{0.25}\text{P}_{0.75}\text{S}_4$  is 0.21 V vs. lithium,

which is close to the measured oxidation potential of chemically similar  $\text{Li}_{10}\text{GeP}_2\text{S}_{12}$ .<sup>48</sup> In addition, the oxidation potential of LISICONS was found to correlate strongly with computed anion band center (goodness of fits  $R^2 = 0.97$ ) and to a lesser extent with lithium band center (goodness of fits  $R^2 = 0.92$ , Fig. S8a, ESI<sup>†</sup>) and total band center (goodness of fits  $R^2 = 0.93$ , Fig. S8b, ESI<sup>†</sup>). There was no correlation between the reduction potential and the phonon band centers (Fig. S8c–e, ESI<sup>†</sup>), whose physical origin requires further studies. We also seek correlation between oxidation potential and oxygen/sulphur p-band center which have been used to understand the stability of perovskites under oxygen evolution reaction condition.<sup>49</sup> However, as can be seen from Fig. S9a and b (ESI<sup>†</sup>), there is no clear correlation between p-band center and the oxidation potential or the anion band center although we can note that the oxidation potential is largely determined by the anion chemistry (oxides vs. sulfides) as reported previously in the literature<sup>41</sup> and that oxides tend to have lower anion p-band center than sulfides as expected. It should be noted that the absence of correlation might also be due, at least partly, to the uncertainty in the computed p-band center arising from the underestimation of DFT band gap in these insulating compounds.<sup>33</sup> Therefore, the anion band center is proposed as one descriptor for electrochemical oxidation stability of lithium ion conductors.


Of significance, fast lithium ion conductors<sup>18</sup> based on LISICONS such as  $\text{Li}_{3.25}\text{Ge}_{0.25}\text{P}_{0.75}\text{S}_4$  have low enthalpy of lithium ion migration and softened lithium phonon DOS, which is accompanied with downshifted anion band center (Fig. S8f, ESI<sup>†</sup>). The correlation between lowered migration barrier with softened average lithium vibration frequency in Fig. 5b, and that between lowered oxidative stability with softened average anion vibration frequency in Fig. 6 highlight a trade-off between lithium ion mobility and oxidation stability for the design of lithium ion conductors. Moreover, extending the concept in Fig. 1a to anion mobility, lowered anion band centers can be accompanied by increased anion mobility, which can promote any solid-state reaction kinetics with electrode materials. Therefore, the interplay between lattice dynamics and ion mobility and stability highlights the need and opportunities to search for fast lithium ion conductors having low lithium band center but high anion band center which exhibit high ion conductivity and high oxidative stability in lithium ion batteries.

### Overcoming the trade-off between mobility and stability

In search of lithium ion conductors with such lattice dynamics characteristics, we further examine Olivines that have the same hexagonal anion sublattice as the LISICON structure (Fig. 7c). The computed enthalpy of lithium ion migration and lithium band center for all the stoichiometric Olivines without transition metal ions listed in the ICSD (except  $\text{LiCdPO}_4$ ,  $\text{LiScGeO}_4$  and  $\text{LiTmSiO}_4$ ) are included in Fig. 7a, which demonstrates lithium band center as descriptor for lithium ion mobility in the two structural families (LISICONS and Olivines). Olivines, exhibit low lithium band centers and migration barriers comparable to that of LISICON thiophosphates (Fig. 7a) but high anion band centers comparable to those of LISICON phosphates (Fig. 7b).





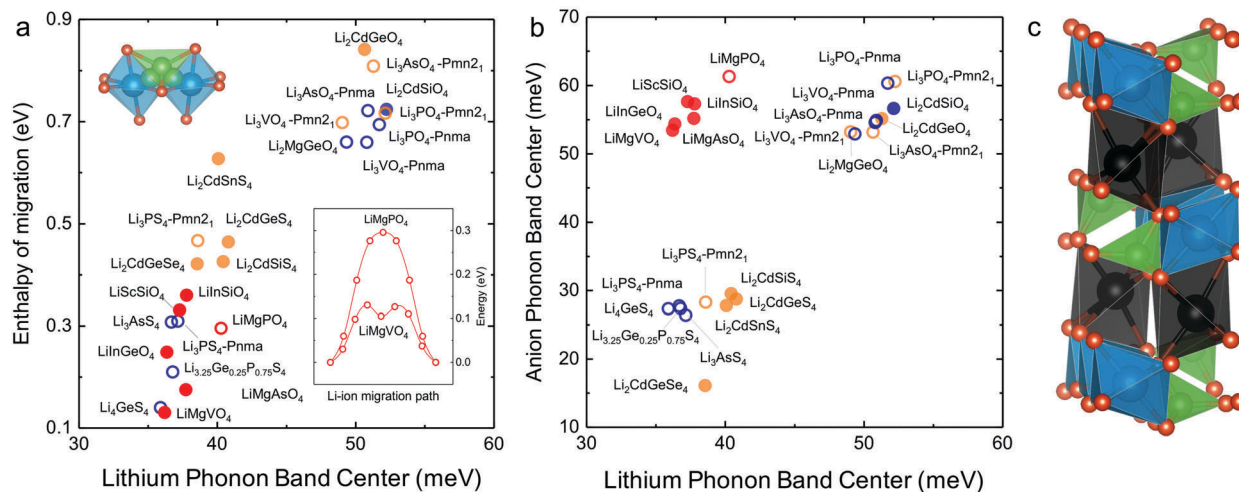

**Fig. 7** (a) Correlation between computed Li-band center and the computed enthalpy of migration including the Olivine structure. (b) Anion band centers and Li-band centers of Olivine compounds compared to LISICON compounds. (c) The Olivine is closely related to the LISICON structure by the fact that both have hexagonal anion sublattice but Li occupy octahedral interstice in Olivine unlike tetrahedral sites in LISICON. The jump sequence used to compute the migration barrier as well as the minimum energy pathway associated with this jump sequence in Olivine are shown in the inset. The enthalpy of migration in olivine was found to be lower than in LISICON. All the computed enthalpies of migration were calculated using the standard climbing image nudge elastic band method<sup>56</sup> and the phonon band center is defined as the average phonon frequency weighted by phonon DOS. The blue and orange colours refer respectively to the HT phase (space group  $Pmna$ ) and the LT phase (space group  $Pmn2_1$ ), respectively while the red colour refers to the Olivine compounds. The filled circles are compounds that are known in the ICSD and/or computed in this work, where the lithium ion conductivity has not been measured experimentally. For more details, please refer to Table S1 (ESI<sup>†</sup>).

Computed migration barriers of Olivines studied here such as  $\text{LiMgPO}_4$  are comparable to those of other Olivine materials such as  $\text{LiMPO}_4$  ( $M = \text{Mn, Fe, Co and Ni}$ , 0.1–0.4 eV)<sup>50</sup> and  $\text{LiMXO}_4$  (main group  $M^{2+}-X^{5+}$ ,  $M^{2+}-X^{5+}$ ;  $M = \text{Mg, Ca, Sr, Ba, Sc, Y, Al, In, Ga}$  and rare-earth elements;  $X = \text{Si, Ge, Sn, P, As and Sb}$ ).<sup>51</sup> In addition, the computed migration barrier ( $\sim 0.3$  eV) of  $\text{LiMgPO}_4$  is in good agreement with NMR measurements for the site-to-site hopping (0.3–0.5 eV).<sup>52</sup> Generally speaking, while compounds having high Li conductivity tend to have low stability, Olivine family was found to be an exception to this trend, which was rationalized in terms of the low Li-band center but high anion band center in these compounds (Fig. 7b). For example, new compositions such as  $\text{LiMgAsO}_4$  and  $\text{LiInGeO}_4$  could potentially have high ion conductivity (Fig. 7a) and stability (Fig. S10, ESI<sup>†</sup>). Unfortunately, the one-dimensional nature of diffusion pathway in the olivine structure makes it prone to anti-site defects which can result in an apparent activation energy much higher than the intrinsic migration barrier.<sup>53</sup> For example, the long-range diffusion barrier measured by EIS for  $\text{LiMgPO}_4$  is 0.7–1.0 eV in previous work<sup>52</sup> and also in this study, much higher than the intrinsic migration barrier ( $\sim 0.3$  eV). Further studies are needed to increase the long-range ion conductivity of these Olivines by reducing anti-site defects using smaller particle sizes<sup>54</sup> and/or having Li-excess in the lattice,<sup>55</sup> which would potentially lead to the development of lithium superionic conductors with high stability against electrochemical oxidation.

## Conclusion

In this study, we account for the first time, the trend in ionic mobility and electrochemical oxidation stability of lithium ion

conductors from one common physical origin, lattice dynamics, or more precisely, atomic vibrational frequencies of ion conductor constituents, thus highlighting the critical role played by the lattice dynamics in governing the lithium ion conductivity and stability of lithium-ion conductors. Unlike previous studies on lattice dynamics in ion conductors (especially  $\text{Ag}^+$  conductors) which focus on the total phonon DOS (such low-energy peak in  $\alpha\text{-AgI}$  phonon DOS) or zone-center phonons as measured from infrared and Raman spectroscopy,<sup>56,57</sup> our study clarifies the influence of lattice dynamics on ionic conductivity by separating the effect of different sublattice and in particular the special role of the mobile species sublattice dynamics in the observed ionic mobility. The phonon DOS have been collected from a series of lithium conductors in the LISICON family using INS and computed by first-principles simulations to identify specific spectral features corresponding to the vibrations of sublattices involving lithium, anion and nonmobile structural cations. Replacing oxygen with sulfur greatly downshifts the lithium vibration frequencies while aliovalent cation substitution tends to broaden the lithium vibrational features in the phonon DOS. We show that low vibration frequencies of lithium ions correlate with enhanced lithium ion mobility in the LISICON and Olivine families, which can be used as one lithium ion mobility descriptor to predict new fast lithium conductors. Recent work on Argyrodite lithium conductors also showed the influence of lattice dynamics on the ionic conductivity.<sup>58</sup> Future work is needed to define a more refined descriptor that would take into account not only the vibration frequency but also the vibrational pattern of each mode and weight in a way that reflects its importance to lithium diffusion as the measured and computed band centers or the average vibrational frequencies





determined in this study do not explicitly take into account the specific vibration pattern of each mode. In addition, future experimental and computational studies should exploit the interplay between lattice dynamic and ion conductivity and stability for lithium ion conductors of different structural families<sup>21</sup> beyond LISICON and Olivine. Moreover, further studies are needed to extend and examine the universality of such descriptors based on lattice dynamics to understand and potentially control ion mobility and stability of other ionic conductors such as Na<sup>+</sup>, Cu<sup>+</sup> or O<sup>2-</sup> conductors. For example, copper sulfide (Cu<sub>2-x</sub>Se) with superionic Cu<sup>+</sup> conductivity at room temperature is known to have low-energy phonon DOS and lattice thermal conductivity.<sup>59</sup> Lattice dynamics was also found to play important role in the Na<sup>+</sup> conductors Na<sub>3</sub>PS<sub>4-x</sub>Se<sub>x</sub><sup>60</sup> as well as O<sup>2-</sup> conductors Nd<sub>2</sub>NiO<sub>4+δ</sub><sup>61</sup> and brownmillerites Sr(Fe,Co)O<sub>2.5</sub>.<sup>62</sup> Lastly, although extensive database for material phonon DOS is not yet available due to high computational cost to compute phonon DOS, recent study has shown that it is possible to use a machine learning model to predict phonon-related properties such as vibrational free energy and entropy with high accuracy at a greatly reduced computational cost.<sup>63</sup> Future advance in machine-learning computational material design represents an exciting opportunity to use this approach to explore more compositional space and to discover new ion conductors.<sup>64-66</sup>

## Author contributions

S. M., Y. S.-H. and J. C. B. proposed the concept. J. C. B. and H.-H. C. prepared the oxide materials. R. K. provided the sulphides samples. S. M., J. C. B., D. B. and O. D. performed the phonon DOS measurements and analysis. S. M. performed all the DFT calculations with L. G.'s help for the NEB calculations. S. M. and Y. S.-H. wrote the manuscript. All authors contributed to the discussion and revision of the manuscript.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

Research at MIT was supported by BMW. J. C. B. was supported in part from the National Science Foundation Graduate Research Fellowship (1122374) and H.-H. C. was in part supported from the Ministry of Science and Technology of Taiwan (102-2917-I-564-006-A1). D. B. acknowledges funding from the U.S. Department of Energy, Office of Science, Basic Energy Sciences, Materials Sciences and Engineering Division, under the Early Career Award No. DE-SC0016166 (P. I. Delaire). This work made use of the MRSEC Shared Experimental Facilities at MIT, supported by the National Science Foundation under award number DMR-0819762. The use of Oak Ridge National Laboratory's Spallation Neutron Source was sponsored by the Scientific User Facilities Division, Office of Basic Energy Sciences, U.S. DOE. This research used resources of the National Energy Research Scientific Computing

Center (NERSC), a DOE Office of Science User Facility supported by the Office of Science of the U.S. Department of Energy under Contract No. DE-AC02-05CH11231 and of the Extreme Science and Engineering Discovery Environment (XSEDE) which is supported by National Science Foundation grant number ACI-1548562.

## References

- 1 K. Xu, *Chem. Rev.*, 2004, **104**, 4303–4418.
- 2 J. B. Goodenough and Y. Kim, *Chem. Mater.*, 2010, **22**, 587–603.
- 3 M. Armand and J.-M. Tarascon, *Nature*, 2008, **451**, 652–657.
- 4 J. Janek and W. G. Zeier, *Nat. Energy*, 2016, **1**, 16141.
- 5 W. Li, L. Chen, Y. Sun, C. Wang, Y. Wang and Y. Xia, *Solid State Ionics*, 2017, **300**, 114–119.
- 6 N. Kamaya, K. Homma, Y. Yamakawa, M. Hirayama, R. Kanno, M. Yonemura, T. Kamiyama, Y. Kato, S. Hama, K. Kawamoto and A. Mitsui, *Nat. Mater.*, 2011, **10**, 682–686.
- 7 Y. Kato, S. Hori, T. Saito, K. Suzuki, M. Hirayama, A. Mitsui, M. Yonemura, H. Iba and R. Kanno, *Nat. Energy*, 2016, 16030.
- 8 P. Bron, S. Johansson, K. Zick, J. Schmedt auf der Günne, S. Dehnen and B. Roling, *J. Am. Chem. Soc.*, 2013, **135**, 15694–15697.
- 9 Y. Seino, T. Ota, K. Takada, A. Hayashi and M. Tatsumisago, *Energy Environ. Sci.*, 2014, **7**, 627–631.
- 10 A. Rodger, J. Kuwano and A. West, *Solid State Ionics*, 1985, **15**, 185–198.
- 11 Y. Deng, C. Eames, B. Fleutot, R. David, J.-N. Chotard, E. Suard, C. Masquelier and M. S. Islam, *ACS Appl. Mater. Interfaces*, 2017, **9**, 7050–7058.
- 12 V. Thangadurai, S. Narayanan and D. Pinzaru, *Chem. Soc. Rev.*, 2014, **43**, 4714–4727.
- 13 A. Martínez-Juárez, C. Pecharróman, J. E. Iglesias and J. M. Rojo, *J. Phys. Chem. B*, 1998, **102**, 372–375.
- 14 S. Stramare, V. Thangadurai and W. Weppner, *Chem. Mater.*, 2003, **15**, 3974–3990.
- 15 J. Auvergniot, A. Cassel, J.-B. Ledeuil, V. Viallet, V. Seznec and R. Dedryvère, *Chem. Mater.*, 2017, **29**, 3883–3890.
- 16 W. D. Richards, L. J. Miara, Y. Wang, J. C. Kim and G. Ceder, *Chem. Mater.*, 2016, **28**, 266–273.
- 17 S. P. Ong, Y. Mo, W. D. Richards, L. Miara, H. S. Lee and G. Ceder, *Energy Environ. Sci.*, 2013, **6**, 148.
- 18 R. Kanno and M. Murayama, *J. Electrochem. Soc.*, 2001, **148**, A742–A746.
- 19 R. Kanno, T. Hata, Y. Kawamoto and M. Irie, *Solid State Ionics*, 2000, **130**, 97–104.
- 20 M. Tachez, J.-P. Malugani, R. Mercier and G. Robert, *Solid State Ionics*, 1984, **14**, 181–185.
- 21 J. C. Bachman, S. Muy, A. Grimaud, H.-H. Chang, N. Pour, S. F. Lux, O. Paschos, F. Maglia, S. Lupart, P. Lamp, L. Giordano and Y. Shao-Horn, *Chem. Rev.*, 2016, **116**, 140–162.
- 22 M. Avdeev, M. Sale, S. Adams and R. P. Rao, *Solid State Ionics*, 2012, **225**, 43–46.
- 23 Y. Wang, W. D. Richards, S. P. Ong, L. J. Miara, J. C. Kim, Y. Mo and G. Ceder, *Nat. Mater.*, 2015, **14**, 1026–1031.



- 24 Y.-W. Hu, I. D. Raistrick and R. A. Huggins, *J. Electrochem. Soc.*, 1977, **124**, 1240–1242.
- 25 Z. Deng, B. Radhakrishnan and S. P. Ong, *Chem. Mater.*, 2015, **27**, 3749–3755.
- 26 Z. Deng, Z. Zhu, I.-H. Chu and S. P. Ong, *Chem. Mater.*, 2017, **29**, 281–288.
- 27 M. T. Dove, *Introduction to Lattice Dynamics*, Cambridge University Press, Cambridge, New York, 1st edn, 2005.
- 28 U. Köhler and C. Herzig, *Philos. Mag. A*, 1988, **58**, 769–786.
- 29 X. Li and N. A. Benedek, *Chem. Mater.*, 2015, **27**, 2647–2652.
- 30 K. Wakamura, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1997, **56**, 11593–11599.
- 31 Y. Deng, C. Eames, J.-N. Chotard, F. Lalère, V. Seznec, S. Emge, O. Pecher, C. P. Grey, C. Masquelier and M. S. Islam, *J. Am. Chem. Soc.*, 2015, **137**, 9136–9145.
- 32 Y. A. Du and N. A. W. Holzwarth, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2007, **76**, 174302.
- 33 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.
- 34 G. Kresse and J. Furthmüller, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1996, **54**, 11169–11186.
- 35 P. E. Blöchl, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1994, **50**, 17953–17979.
- 36 G. Henkelman, B. P. Uberuaga and H. Jónsson, *J. Chem. Phys.*, 2000, **113**, 9901–9904.
- 37 R. Wahl, D. Vogtenhuber and G. Kresse, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2008, **78**, 104116.
- 38 A. Togo and I. Tanaka, *Scr. Mater.*, 2015, **108**, 1–5.
- 39 A. Jain, S. P. Ong, G. Hautier, W. Chen, W. D. Richards, S. Dacek, S. Cholia, D. Gunter, D. Skinner, G. Ceder and K. A. Persson, *APL Mater.*, 2013, **1**, 011002.
- 40 S. P. Ong, W. D. Richards, A. Jain, G. Hautier, M. Kocher, S. Cholia, D. Gunter, V. L. Chevrier, K. A. Persson and G. Ceder, *Comput. Mater. Sci.*, 2013, **68**, 314–319.
- 41 Y. Zhu, X. He and Y. Mo, *J. Mater. Chem. A*, 2016, **4**, 3253–3266.
- 42 H. Böttger, *Principles of the Theory of Lattice Dynamics*, Physik-Verlag, 1983.
- 43 Y. Du and N. Holzwarth, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2008, **78**, 174301.
- 44 K. M. Mishra, A. K. Lal and F. Z. Haque, *Solid State Ionics*, 2004, **167**, 137–146.
- 45 I. M. Hodge, M. D. Ingram and A. R. West, *J. Am. Ceram. Soc.*, 1976, **59**, 360–366.
- 46 T. T. Mayeshiba and D. D. Morgan, *Solid State Ionics*, 2016, **296**, 71–77.
- 47 X. He, Y. Zhu and Y. Mo, *Nat. Commun.*, 2017, **8**, ncomms15893.
- 48 F. Han, Y. Zhu, X. He, Y. Mo and C. Wang, *Adv. Energy Mater.*, 2016, **6**, 1501590.
- 49 A. Grimaud, K. J. May, C. E. Carlton, Y.-L. Lee, M. Risch, W. T. Hong, J. Zhou and Y. Shao-Horn, *Nat. Commun.*, 2013, **4**, 2439.
- 50 D. Morgan, A. V. der Ven and G. Ceder, *Electrochem. Solid-State Lett.*, 2004, **7**, A30–A32.
- 51 R. Jalem, T. Aoyama, M. Nakayama and M. Nogami, *Chem. Mater.*, 2012, **24**, 1357–1364.
- 52 L. Enciso-Maldonado, M. S. Dyer, M. D. Jones, M. Li, J. L. Payne, M. J. Pitcher, M. K. Omir, J. B. Claridge, F. Blanc and M. J. Rosseinsky, *Chem. Mater.*, 2015, **27**, 2074–2091.
- 53 R. Malik, D. Burch, M. Bazant and G. Ceder, *Nano Lett.*, 2010, **10**, 4123–4127.
- 54 C. Delacourt, P. Poizot, S. Levasseur and C. Masquelier, *Electrochem. Solid-State Lett.*, 2006, **9**, A352–A355.
- 55 K.-Y. Park, I. Park, H. Kim, G. Yoon, H. Gwon, Y. Cho, Y. S. Yun, J.-J. Kim, S. Lee, D. Ahn, Y. Kim, H. Kim, I. Hwang, W.-S. Yoon and K. Kang, *Energy Environ. Sci.*, 2016, **9**, 2902–2915.
- 56 R. Alben and G. Burns, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1977, **16**, 3746–3752.
- 57 P. Brüesch, W. Bührer and H. J. M. Smeets, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1980, **22**, 970–981.
- 58 M. A. Kraft, S. P. Culver, M. Calderon, F. Böcher, T. Krauskopf, A. Senyshyn, C. Dietrich, A. Zevalkink, J. Janek and W. G. Zeier, *J. Am. Chem. Soc.*, 2017, **139**, 10909–10918.
- 59 H. Liu, X. Shi, F. Xu, L. Zhang, W. Zhang, L. Chen, Q. Li, C. Uher, T. Day and G. J. Snyder, *Nat. Mater.*, 2012, **11**, 422–425.
- 60 T. Krauskopf, C. Pompe, M. A. Kraft and W. G. Zeier, *Chem. Mater.*, 2017, **29**, 8859–8869.
- 61 A. Perrichon, A. Piovano, M. Boehm, M. Zbiri, M. Johnson, H. Schober, M. Ceretti and W. Paulus, *J. Phys. Chem. C*, 2015, **119**, 1557–1564.
- 62 W. Paulus, H. Schober, S. Eibl, M. Johnson, T. Berthier, O. Hernandez, M. Ceretti, M. Plazanet, K. Conder and C. Lamberti, *J. Am. Chem. Soc.*, 2008, **130**, 16080–16085.
- 63 F. Legrain, J. Carrete, A. van Roekeghem, S. Curtarolo and N. Mingo, *Chem. Mater.*, 2017, **29**, 6220–6227.
- 64 N. Nosengo, *Nat. News*, 2016, **533**, 22.
- 65 S. Curtarolo, G. L. W. Hart, M. B. Nardelli, N. Mingo, S. Sanvito and O. Levy, *Nat. Mater.*, 2013, **12**, 191–201.
- 66 L. Ward and C. Wolverton, *Curr. Opin. Solid State Mater. Sci.*, 2017, **21**, 167–176.
- 67 D. Bansal, J. Hong, C. W. Li, A. F. May, W. Porter, M. Y. Hu, D. L. Abernathy and L. Delaire, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2016, **94**, 054307.
- 68 G. Sahu, Z. Lin, J. Li, Z. Liu, N. Dudney and C. Liang, *Energy Environ. Sci.*, 2014, **7**, 1053.

