


Nanoscale

rsc.li/nanoscale



ISSN 2040-3372

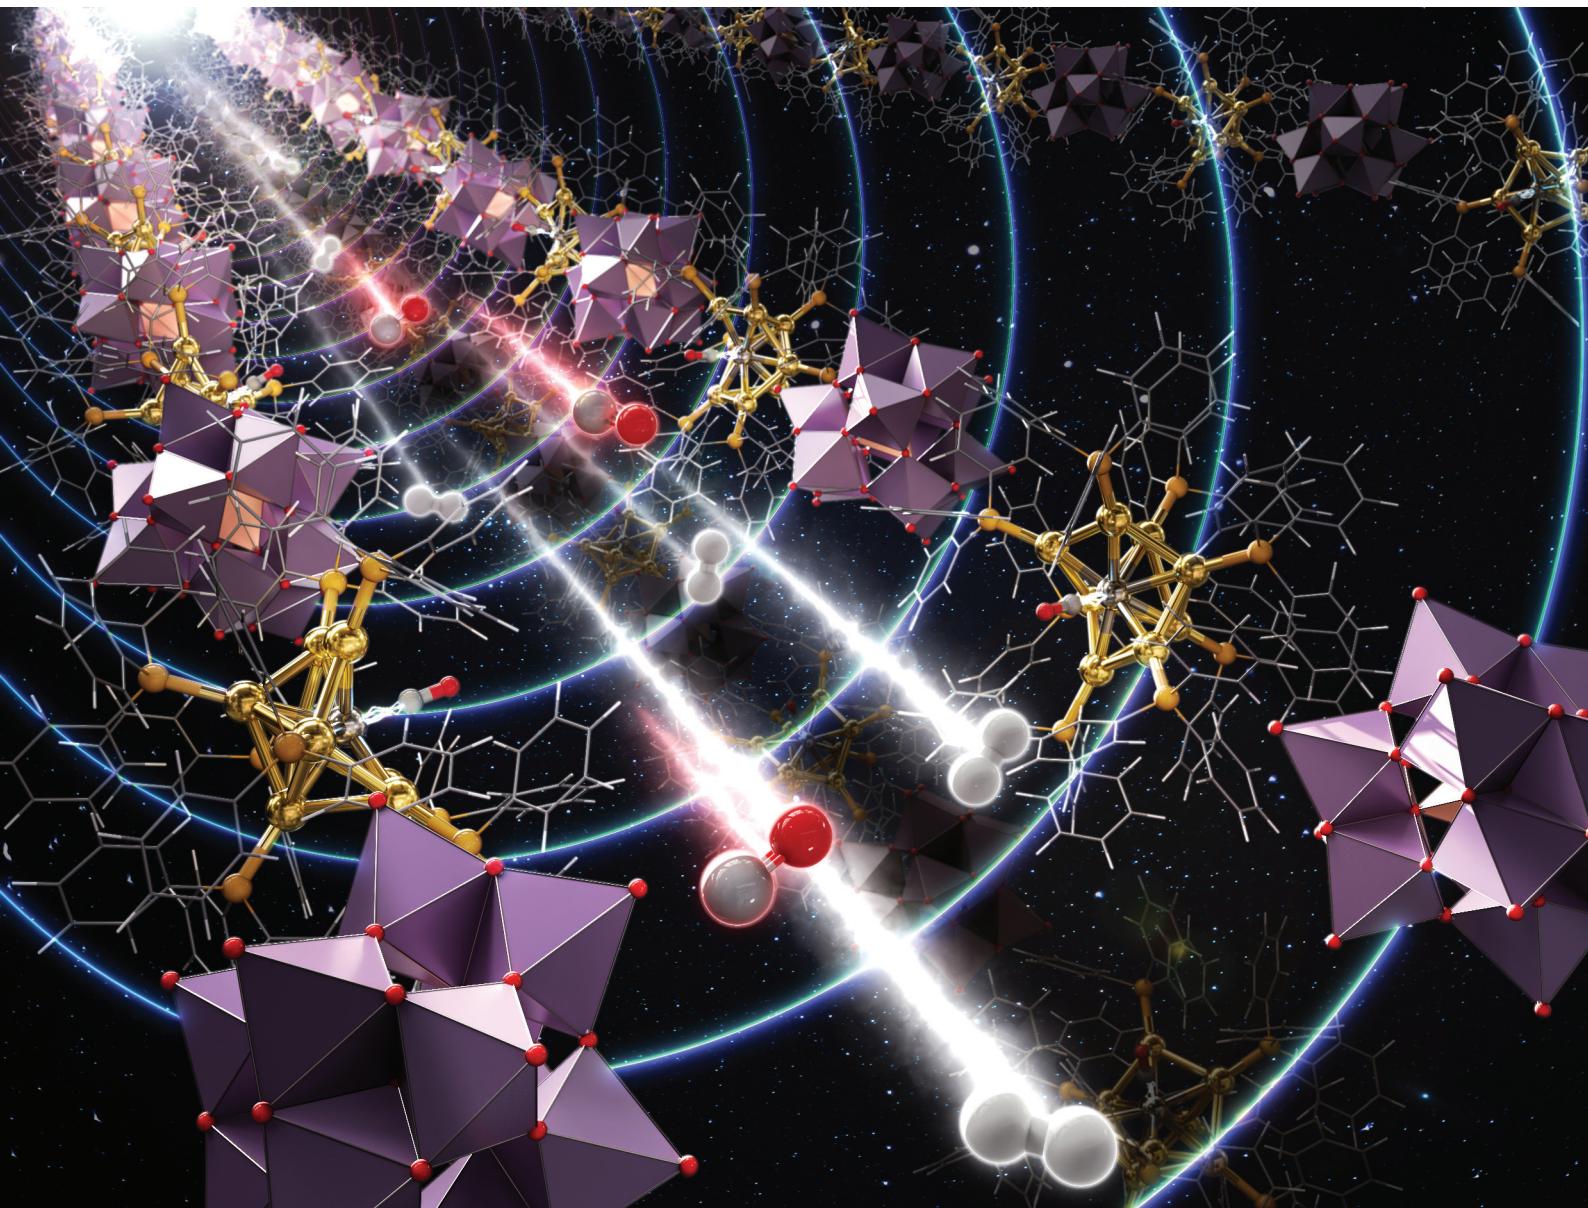

Cite this: *Nanoscale*, 2025, **17**, 2480

In situ QXAFS study of CO and H₂ adsorption on Pt in [PtAu₈(PPh₃)₈]-H[PMo₁₂O₄₀] solid†

Tomoki Matsuyama,^a Taishi Suzuki,^a Yuto Oba,^a Soichi Kikkawa,^{ID a} Sayaka Uchida,^{ID b} Junya Ohyama,^{ID c} Kotaro Higashi,^d Takuma Kaneko,^d Kazuo Kato,^d Kiyofumi Nitta,^d Tomoya Uruga,^d Keisuke Hatada,^e Kazuki Yoshikawa,^e Amelie Heilmaier,^{ID e,f} Kosuke Suzuki,^{ID g} Kentaro Yonesato,^{ID g} Kazuya Yamaguchi,^{ID g} Naoki Nakatani,^{ID a} Hideyuki Kawasoko,^{ID a,h} and Seiji Yamazoe,^{ID *}^a

The adsorption behaviors of H₂ and CO molecules in crown-motif [PtAu₈(PPh₃)₈]-H[PMo₁₂O₄₀] (**PtAu8-PMo12**) solids were investigated by *in situ* quick-scan X-ray absorption fine structure (QXAFS) measurements with a time resolution of 0.1 s. The electronic state of Pt in **PtAu8-PMo12** was drastically changed by the adsorption of H₂ and CO molecules because of the formation of Pt-H₂/Pt-CO interactions. H₂ was adsorbed more rapidly (<0.5 s) on Pt than CO (~2.5 s) and showed reversible adsorption/desorption behavior on Pt atoms in **PtAu8-PMo12**. The rapid adsorption of H₂ is due to the fast diffusion of H₂, which has a smaller kinetic diameter than CO, in the narrow channels between the closed voids in **PtAu8-PMo12**. Meanwhile, CO was irreversibly adsorbed on Pt, resulting in structural isomerization to the stable "chalice-motif" **PtAu8**, which was determined by XAFS analysis and density functional theory calculations. Structural isomerization was involved by pushing ligands aside to make space for CO adsorption as the void size near Pt in the crown-motif **PtAu8-PMo12** was narrower than the kinetic diameter of CO.

Received 14th September 2024,
Accepted 14th November 2024

DOI: 10.1039/d4nr03785e

rsc.li/nanoscale

Introduction

Metal clusters composed of <100 atoms have attracted significant attention because of their quantized electronic states and unique geometric structures that cannot be predicted from their bulk materials.^{1–4} The electronic state of metal clusters,

which determines their functions, depends on the number of metal atoms and their geometric structures. Therefore, atomically precise synthesis of metal clusters is essential to understand the relationship between functions and structures.^{5,6} To date, numerous ligand-protected metal clusters composed of Au, Ag, and Cu, among others, have been synthesized in a liquid phase. For example, Au ions are reduced in the presence of different protecting ligands, like phosphine,⁷ thiolate,⁸ alkynyl,⁹ and N-heterocyclic carbene,¹⁰ which allows the synthesis of ligand-protected Au clusters with a highly homogeneous size distribution. Ligand-protected Au clusters have unique electronic structures depending on their size and composition, and exhibit optical properties,^{11,12} photoluminescence,¹³ magnetism,¹⁴ and redox activity.¹⁵

The ligand-protected metal clusters have been applied as catalysts, such as for the selective oxidation of styrene by phosphine-protected Au₁₁(PR₃)₇Cl₃ and [Au₁₁(PR₃)₈Cl₂]⁺ (R = alkyl groups)¹⁶ or by thiolate-protected Au₂₅(SR)₁₈, Au₃₈(SR)₂₄ and Au₁₄₄(SR)₆₀¹⁷ as well as methane oxidation by mixed ligand-protected [Au₂₄(PR₃)₁₀(SR)₅Cl₂][–] and [Au₂₅(PR₃)₁₀(SR)₅Cl₂]^{2–}.¹⁸ Heterometal doping is one of the most effective methods for controlling and inducing the reactivities of ligand-protected Au clusters because metal dopants can modulate the electronic state of the clusters. The hydrogen evolution reaction has been accelerated by Pt single-atom doping to [Au₂₅(SR)₁₈][–] because

^aDepartment of Chemistry, Graduate School of Science, Tokyo Metropolitan University, 1-1 Minami-osawa, Hachioji-shi, Tokyo 192-0397, Japan.

E-mail: yamazoe@tmu.ac.jp

^bDepartment of Basic Science, School of Arts and Sciences, The University of Tokyo, 3-8-1 Komaba, Meguro-ku, Tokyo 153-8902, Japan

^cFaculty of Advanced Science and Technology, Kumamoto University, 2-39-1 Kurokami, Chuo-ku, Kumamoto-shi, Kumamoto 860-8555, Japan

^dCenter for Synchrotron Radiation Research, Japan Synchrotron Radiation Research Institute (JASRI), 1-1-1, Kouto, Sayo-cho, Sayo-gun, Hyogo 679-5198, Japan

^eDepartment of Physics, University of Toyama, 3190 Gofuku, Toyama 930-8555, Japan

^fDepartment of Chemistry, Ludwig-Maximilians-Universität (LMU), Butenandtstr. 5-13, 81377 Munich, Germany

^gDepartment of Applied Chemistry, School of Engineering, The University of Tokyo, 7-3-1 Hongo, Bunkyo-ku, Tokyo 113-8656, Japan

^hPrecursory Research for Embryonic Science and Technology (PRESTO), Japan Science and Technology Agency (JST), 7, Gobancho, Chiyoda-ku, Tokyo 102-0076, Japan

† Electronic supplementary information (ESI) available: Fig. S1–S15, Scheme S1 and Tables S1–S3. See DOI: <https://doi.org/10.1039/d4nr03785e>

of the depletion of two valence electrons and a positive shift in reduction potential.¹⁹ Phosphine-protected $\text{MAu}_{12}(\text{PRP})_5\text{Cl}_2$ (M = Au, Pd, Pt, Ru, Rh, Ir) also showed a change in electronic structure depending on the central dopant.²⁰ In particular, photoinduced intermolecular [2 + 2] cycloaddition of bisenone was shown to be promoted by Pt- and Ir-doped $\text{MAu}_{12}(\text{PRP})_5\text{Cl}_2$.²¹ Metal dopants often provide new active sites.

Among the ligand-protected metal clusters, phosphine-protected $[\text{Au}_9(\text{PR}_3)_8]^{3+}$ (**Au9**) with a crown-motif structure has a coordinatively unsaturated Au atom located at the center of **Au9**.²² Although the molecule can access the central Au in **Au9**, no reports have described that the molecule is activated by **Au9**. Meanwhile, $[\text{PtAu}_8(\text{PR}_3)_8]^{2+}$ (**PtAu8**) with a crown-motif structure, in which the central Au in **Au9** is substituted by Pt, worked as a catalyst for the $\text{H}_2\text{-D}_2$ exchange reaction.²³ In addition, **PtAu8** in the solution state exhibited the nucleophilic adsorption of small molecules, such as CO.²⁴ These reactivities have also been reported for Pt-centered Au clusters, such as $[\text{PtAu}_9(\text{PR}_3)_9]^{3+}$ and $[(\text{PR}_3)\text{PtAu}_6(\text{PR}_3)_6]^{2+}$.^{25,26} However, the molecular adsorption on solid ligand-protected metal clusters has been limited.

Our group focused on **Au9** and heterometal-doped $[\text{MAu}_8(\text{PPh}_3)_8]^{2+}$ (**MAu8**, M = Pt, Pd) to investigate thermal stabilities²⁷ and control their geometric structures using counter anions.²⁸ Recently, crown-motif **Au9** and **MAu8** were synthesized by associating anionic $[\text{PMo}_{12}\text{O}_{40}]^{3-}$ (**PMo12**) polyoxometalate with cesium chloride crystal packing structures.²⁷ The **Au9-PMo12** and $[\text{MAu}_8(\text{PPh}_3)_8]\text{-H}[\text{PMo}_{12}\text{O}_{40}]$ (**MAu8-PMo12**) were thermally stable at $<473\text{ K}$.²⁷ The crystal structure of **PtAu8-PMo12** is shown in Fig. 1. Two types of voids of different sizes can be observed in the crystals. The large void (V_L) is in the *ab*-plane, and **PtAu8** is surrounded by $4V_L$. The small void (V_S) is located over the Pt atom in **PtAu8**. H_2 and CO are linear diatomic molecules of different sizes and thus can be used as probe molecules to reveal the reactivity of solid ligand-protected metal clusters in porous crystals with small voids. Interestingly, we found that small molecules, such as H_2 and CO, could diffuse into the **PtAu8-PMo12** solid although

these voids are isolated and there is no path for the molecules to diffuse into the crystal.

This study focuses on the H_2 and CO adsorption/desorption properties of **PtAu8-PMo12** solids. The interaction of the central Pt for **PtAu8** with H_2/CO was monitored by *in situ* quick-scan X-ray absorption fine structure (QXAFS) analysis because the peak intensity and energy assigned to 2p-5d electron transition were changed by the interaction of Pt with the molecule.³⁰ We found that both H_2 and CO could diffuse into **PtAu8-PMo12** solid and interact with Pt of **PtAu8** core, whereas **Au9-PMo12**, which had the same crystal structure as **PtAu8-PMo12**, could not interact with H_2 and CO. The adsorption rate of H_2 on Pt is more than four times higher than that of CO in **PtAu8-PMo12**, suggesting that the diffusion of molecules in **PtAu8-PMo12** solids is a key process for molecular adsorptions and small H_2 can pass through the narrow channels more easily than CO.

Results and discussion

The synthesis of $[\text{PtAu}_8(\text{PR}_3)_8](\text{NO}_3)_2$ (**PtAu8-NO3**) was confirmed by ESI-MS and UV-Vis spectroscopy. As shown in Fig. 2a, a strong divalent molecular ion peak was observed at $m/z = 1935.1$. This isotopic pattern was consistent with the pattern calculated as $[\text{PtAu}_8(\text{PPh}_3)_8]^{2+}$. Fig. 2b shows the UV-Vis spectrum of the **PtAu8-NO3** methanol solution. The broad band at 500–570 nm and the peaks at 428, 354, and 306 nm were in accordance with the absorption properties of the **PtAu8-NO3** solution with the crown-motif structure.³¹ **PtAu8-PMo12** synthesized by anion exchange was characterized by DR-UV-Vis spectroscopy and powder XRD. A broad band at

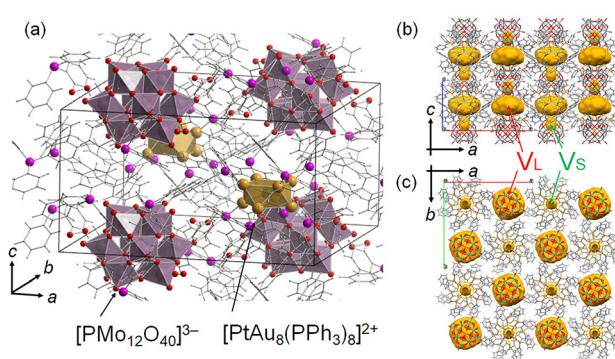


Fig. 1 (a) Crystal structure of **PtAu8-PMo12**.²⁷ Void analysis of **PtAu8-PMo12** in the (b) *ac*-plane and (c) *ab*-plane. Void space (in yellow) is depicted with a probe radius of 1.2 Å using the CSD Mercury software.²⁹

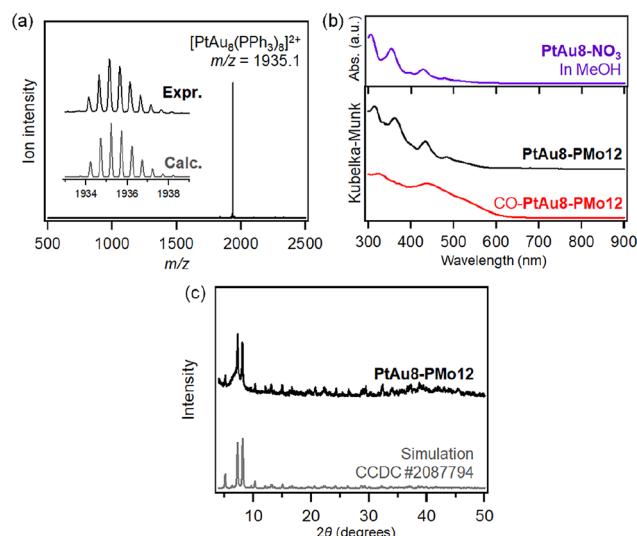


Fig. 2 Characterizations of **PtAu8-NO3** and **PtAu8-PMo12**. (a) Positive-ion mode ESI-MS of the acetonitrile solution of **PtAu8-NO3**. (b) UV-Vis spectrum of methanolic solution of **PtAu8-NO3** and DR-UV-Vis spectra of **PtAu8-PMo12** and CO adsorbed **PtAu8-PMo12**. (c) Powder-XRD patterns of **PtAu8-PMo12** and simulated **PtAu8-PMo12** (CCDC 2087794).

500–570 nm and peaks at 434, 361, and 313 nm observed in the **PtAu8-PMo12** solid were consistent with those of the crown-motif structure.²⁸ The powder XRD pattern of the **PtAu8-PMo12** solid had diffraction peaks at $2\theta = 5.12, 7.25$, and 8.09 degrees, as shown in Fig. 2c. These results indicate that the **PtAu8-PMo12** solid had a CsCl-type crystal structure.²⁸ In addition, local structures of **PtAu8-PMo12** were determined by curve fitting analysis of Au L₃- and Pt L₃-edges EXAFS spectra at 10 K (Fig. S1 and S2[†]). The average coordination numbers (CNs) for Au–P (CN = 1.4 ± 0.2), Au–Pt (CN = 1.4 ± 0.1), and Au–Au bonds (CN = 2.3 ± 0.2) obtained by Au L₃-edge FT-EXAFS analysis, and for Pt–Au (CN = 7.8 ± 0.3) obtained by Pt L₃-edge FT-EXAFS analysis revealed that the **PtAu8** in **PtAu8-PMo12** had a crown-motif structure with the central atom of Pt (Tables S1 and S2[†]). Similar characterizations were conducted for **Au9-PMo12** (Fig. S1, S3 and Table S1[†]). From the above results, we concluded that **PtAu8-PMo12** and **Au9-PMo12** solids with crown-motif structures were synthesized.

We investigated the molecular adsorption properties of crown-motif **PtAu8-PMo12** using Pt L₃-edge XAFS measurements. The Pt L₃-edge XANES of **PtAu8-PMo12** is shown in Fig. 3a. The peak appearing in the absorption edge at 11 569.6 eV was assigned to the electron transition from Pt 2p to unoccupied 5d orbitals.³² The peak energy and intensity were

changed by the introduction of CO, as shown in Fig. 3a. The time course of the peak intensity at 11 570 eV is shown in Fig. 3b. The peak intensity was increased by CO introduction within 2.5 s. The peak energy at the absorption edge shifted from 11 569.6 eV to 11 570.5 eV. These changes are due to the formation of Pt 5d–C 2p antibonding hybrid orbitals and electron donation from Pt to CO upon CO adsorption on the central Pt of the **PtAu8** cluster (discussed later). No shape changes in the Pt L₃-edge XANES were observed upon exposure to a vacuum after CO introduction, as shown in Fig. 3a. Meanwhile, the crown-motif **Au9-PMo12**, which also had a CsCl-type crystal structure (as shown in Fig. S4a[†]) with an Au center in the crown-motif **Au9**, did not adsorb CO under the same conditions because no change in Au L₃-edge XANES and EXAFS was detected before and after CO introduction, as shown in Fig. S4b–d.[†] We also performed Pt L₃-edge *in situ* XANES measurements for **PtAu8-NO3** acetonitrile solution, of which Pt atoms reacted with H₂ and CO (Fig. S5[†]). The XANES spectra of the solution sample showed similar changes in the white line intensity compared with that of solid **PtAu8-PMo12**; thus, we consider that CO and H₂ adsorption on Pt occurs on the crystal surface and inside the crystal. These results suggest that the CO diffuses into solid **PtAu8-PMo12** and strongly interacts with Pt of the crown-motif **PtAu8**.

Because it is known that CO adsorbed on **PtAu8** in solution to form $[\text{Pt}(\text{CO})\text{Au}_8(\text{PPh}_3)_8]^{2+}$,²⁴ the structure of **PtAu8-PMo12** after CO introduction (CO-**PtAu8-PMo12**) was investigated by ESI-MS, UV-Vis, XAFS, and DFT calculations. The ESI-MS spectrum of CO-**PtAu8-PMo12** is shown in Fig. S6.[†] The $[\text{CO}]\text{PtAu}_8(\text{PPh}_3)_8]^{2+}$ was detected, suggesting that CO adsorbed on **PtAu8** in a solid form. The DR-UV-Vis spectra of **PtAu8-PMo12** before and after CO introduction indicated that the optical properties were changed by CO introduction (Fig. 2b), and a peak at 430 nm and shoulder peak at 520 nm appeared. The optical properties of CO-**PtAu8-PMo12** resembled those of $[\text{Pt}(\text{CO})\text{Au}_8(\text{PPh}_3)_8]^{2+}$ in an ethanol solution, as shown in Fig. S7.[†] The stable structure of CO-adsorbed **PtAu8** (CO-**PtAu8**) calculated by DFT is shown in Fig. 3c. The stable structure, with a “chalice-motif” structure, was in accordance with $[\text{Pt}(\text{CO})\text{Au}_8(\text{PPh}_3)_8]^{2+}$ in solution, as reported previously.²⁴ The absorption peaks of CO-**PtAu8-PMo12** at 430 and 530 nm were reproduced by TDDFT calculations using the calculated CO-**PtAu8** structure, as shown in Fig. S7.[†] Au L₃- and Pt L₃-edge EXAFS and FT-EXAFS revealed that the crown-motif structure of **PtAu8-PMo12** was changed by CO introduction, as shown in Fig. S8.[†] Curve fitting analysis revealed that CNs and the bonding distances of Au–P ($1.0 \pm 0.2, 2.23 \pm 0.03 \text{ \AA}$), Au–Pt ($1.3 \pm 0.1, 2.69 \pm 0.02 \text{ \AA}$), and Au–Au ($3.6 \pm 0.7, 2.93 \pm 0.11 \text{ \AA}$) in Au L₃-edge and CNs and the bonding distances of Pt–C ($1.3 \pm 0.3, 1.81 \pm 0.10 \text{ \AA}$), Pt–Au ($8.0 \pm 0.4, 2.64 \pm 0.03 \text{ \AA}$) in Pt L₃-edge of CO-**PtAu8-PMo12** agreed with those obtained from the calculated CO-**PtAu8**, as shown in Tables S1, S2 and S3.[†] In addition, the absorption edge peak appearing in the Pt L₃-edge XANES shifted to a high-energy region by CO adsorption (Fig. 3a). The simulated Pt L₃-edge XANES of the crown-motif **PtAu8** and the chalice-motif CO-**PtAu8** (using the structure in

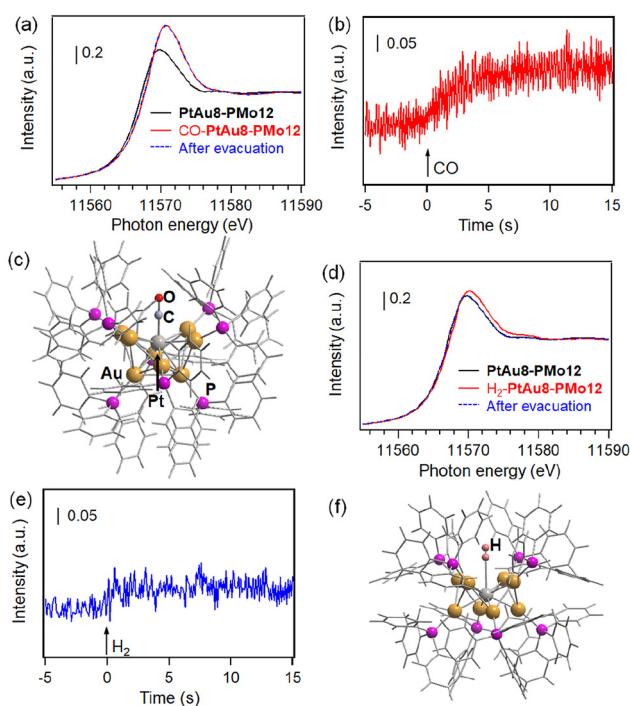


Fig. 3 (a) Pt L₃-edge XANES spectra of **PtAu8-PMo12**, CO-introduced **PtAu8-PMo12**, and after evacuation. (b) Time course of peak intensity at 11 570 eV in Pt L₃-edge XANES of **PtAu8-PMo12** during CO introduction. (c) Optimized structure of CO-**PtAu8** by DFT calculation. (d) Pt L₃-edge XANES spectra of **PtAu8-PMo12**, H₂-introduced **PtAu8-PMo12**, and after evacuation. (e) Time course of peak intensity at 11 570 eV in Pt L₃-edge XANES of **PtAu8-PMo12** during H₂ introduction. (f) Optimized structure of H₂-**PtAu8** by DFT calculation.

Fig. 3c) revealed that the peaks in the absorption edge of CO-**PtAu8** appeared at a higher-energy region than those of the crown-motif **PtAu8** (Fig. S9†). These results indicate that CO diffused into the **PtAu8-PMo12** solid and that one CO was adsorbed on the central Pt of **PtAu8**.

H_2 adsorption behavior was also investigated by Pt L₃-edge XANES of **PtAu8-PMo12** solids. The Pt L₃-edge XANES spectra of **PtAu8-PMo12** before and after H_2 introduction are shown in Fig. 3d. The peak at 11 569.6 eV was slightly shifted to 11 570.2 eV and increased by H_2 introduction because of the formation of the hybrid orbital of Pt 5d-H 1s.³⁰ The time course of peak intensity at 11 570 eV is shown in Fig. 3e. Interestingly, the peak intensity was immediately changed within 500 ms by H_2 introduction, which was faster than that of CO adsorption. The Pt L₃-edge XANES of **PtAu8-PMo12** returned to its original state after H_2 evacuation, as shown in Fig. 3d. After H_2 evacuation, H_2 was reintroduced into **PtAu8-PMo12**. The H_2 again interacted with Pt within 500 ms, and the Pt L₃-edge XANES of the second H_2 -adsorbed **PtAu8-PMo12** was in good agreement with that of the first one. The changes in Pt L₃-edge XANES shape corresponding to the H_2 adsorption and desorption were repeated four times, as shown in Fig. S10.† Meanwhile, the crown-motif **Au9-PMo12**, as shown in Fig. S4,† did not interact with H_2 under the same conditions because no change in Au L₃-edge XANES was detected before and after H_2 introduction, as shown in Fig. S11.† Therefore, we found that H_2 adsorption/desorption proceeded reversibly on Pt in **PtAu8-PMo12**.

The structure of H_2 -adsorbed **PtAu8** in **PtAu8-PMo12** was investigated by Au L₃-edge EXAFS, as shown in Fig. S12.† Changes in the EXAFS oscillations of **PtAu8-PMo12** before and after H_2 adsorption were not observed. The DFT calculation of H_2 adsorption on Pt at end-on while maintaining the crown-motif **PtAu8** in Fig. 3f also demonstrated that there was no conformational change due to H_2 adsorption.

Next, the diffusion of CO and H_2 molecules into **PtAu8-PMo12** solids is discussed. **PtAu8-PMo12** possesses two types of closed voids, V_L (8.9 Å × 8.9 Å × 5.3 Å) and V_S (3.1 Å × 3.1 Å × 4.0 Å), as shown in Fig. 1 and S13.† The large void, V_L , is in the *ab*-plane, and **PtAu8** is surrounded by four V_L . The small void, V_S , is located over the Pt atom in **PtAu8**. Considering that the kinetic diameters of H_2 and CO, which are empirically used for gas adsorption, are 2.89 Å and 3.76 Å, respectively,³³ V_L has a sufficient size for both H_2 and CO, whereas V_S can only accept H_2 . Interestingly, the neighbouring V_L - V_L in the *ab*-plane and V_L - V_S in the *ac*- or *bc*-plane are connected by a narrow channel (diameter of 1.6–2.2 Å), as shown in Fig. 4. Uchida's group reported that an ionic crystal composed of polyoxometalate and metal complex could absorb Cs⁺ (ion radius: 3.1 Å) by the diffusion between the closed voids due to the flexibility of the crystal lattice.³⁴ Identically, H_2 and CO can reach Pt of **PtAu8** by diffusing between the closed voids through the narrow channels, as shown in Fig. 4, owing to the flexibility of the ligands of **PtAu8**. After the molecules diffuse into the V_L in the *ab*-plane through narrow **path 1** in Fig. 4, some of the molecules move to V_S through **path 2** in Fig. 4. In

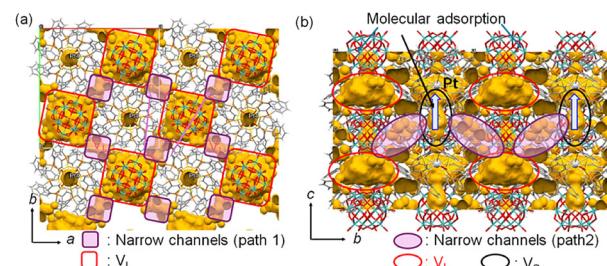


Fig. 4 Void spaces and narrow channels in **PtAu8-PMo12**: views of (a) *ab*- and (b) *bc*-planes. A probe radius of 0.8 Å was used to visualize the narrow channels.

the case of H_2 adsorption/desorption, the V_S over **PtAu8**, which is the void through which Pt is accessed, is larger than H_2 . Therefore, H_2 adsorbs/desorbs on/from Pt without structural changes. Pignolet's group reported that the H_2 -D₂ exchange reaction proceeded on the Pt of **PtAu8**.²³ However, they did not determine the adsorption site of H_2 experimentally or mention the H_2 diffusion into a solid. We demonstrated that H_2 diffused into the **PtAu8-PMo12** solid and was adsorbed on Pt in **PtAu8** without structural change.

We also demonstrated that CO, which is larger than H_2 , diffused into the **PtAu8-PMo12** solid and adsorbed on Pt, despite the V_S being smaller than a CO molecule. Because the adsorbed CO did not desorb under vacuum conditions (Fig. 3a), CO was strongly adsorbed on Pt. Therefore, it is expected that the crown-motif structure isomerized to the chalice-motif structure to make space to adsorb CO on Pt, as shown in Fig. 3c. Steggerda's group reported that CO reacted with **PtAu8** in solution to obtain the chalice-motif [Pt(CO)Au₈(PPh₃)₈]²⁺.²⁴ In addition, the structural isomerization from crown-motif to chalice-motif is achieved by small changes in cluster size and (3AuPPh₃)-Pt-(3AuPPh₃) angle, as shown in Scheme S1.† Therefore, the chalice-motif [Pt(CO)Au₈(PPh₃)₈]²⁺ can be formed by CO adsorption on crown-motif **PtAu8-PMo12** with structural isomerization even in the solid phase.

The *in situ* QXAFS measurements revealed that H_2 adsorption on Pt of **PtAu8-PMo12** occurred faster than CO adsorption, as shown in Fig. 3b and e. The adsorption rate depends on the adsorption energy and/or diffusion path. The adsorption/desorption studies clearly showed that the interaction between H_2 and Pt was weaker than that between CO and Pt because H_2 was reversibly adsorbed/desorbed, whereas CO was not desorbed under the same conditions. The H_2 adsorption energy (difference in the Gibbs free energies) on Pt of the crown-motif **PtAu8** was calculated to be a positive value (0.33 eV) due to the effect of entropy because the difference in the adsorption enthalpies was -0.035 eV, which was similar to H_2 adsorption energies on metal clusters.³⁵ The Pt-H bond length of 2.902 Å in H_2 -**PtAu8** is longer than the Pt-H bond (1.646 Å) in hydride-adsorbed H-**PtAu8**³⁶ calculated by DFT, as shown in Fig. S14.† Therefore, the interaction between H_2 and **PtAu8** is weak, and adsorbed H_2 is desorbed under vacuum conditions.

The reason that the CO did not desorb from **PtAu8-PMo12** under vacuum conditions is that the CO adsorption energy was calculated to be -0.73 eV, which means that CO-**PtAu8** is more stable than crown-motif **PtAu8** with CO and is the driving force for structural isomerization. The calculated Pt-CO length of 1.91 Å in CO-**PtAu8** is in the range of typical coordination bonds. Therefore, CO adsorption occurs as chemisorption, while H₂ adsorption occurs as physisorption. These results clearly explained the trends between H₂ and CO adsorption/desorption although the H₂ adsorption rate was not explained by the adsorption energy.

The molecular diffusion in a solid depends on the diffusion path, void size, and molecular size. From the above discussion, there is no difference in the diffusion path through which the two molecules diffuse. However, molecules must pass through the narrow channels (**paths 1** and **2**) with a diameter of 1.6 – 2.2 Å to reach the Pt sites in **PtAu8-PMo12**. Because the kinetic diameter of H₂ (2.89 Å) is smaller than that of CO (3.76 Å), H₂ diffuses in the narrow channel more easily than CO. In addition, CO needs to push the ligands aside to make space for adsorption on Pt because the V_S is narrower than the kinetic diameter of CO. We concluded that the molecular adsorption rate in **PtAu8-PMo12** depends on the diffusion between closed voids and that the smaller molecule, H₂, shows more rapid adsorption on Pt in **PtAu8-PMo12** than CO, which must make space for adsorption by pushing ligands aside.

This work indicates that the gas diffusion rates of H₂ and CO of **PtAu8-PMo12** differ due to the size of the molecules and voids. In addition, we demonstrated that the optical properties of the clusters could be changed by CO adsorption with structural isomerization. The void size was controlled by the combination of cationic ligand-protected metal clusters and anionic metal oxide clusters with different sizes and compositions. Thus, the void-engineering of composite clusters and/or control of optical properties by molecular adsorption leads to the development of gas separation and/or gas sensors.

Conclusions

In this study, we investigated the molecular adsorption behaviors of crown-motif **PtAu8-PMo12** solid by *in situ* QXAFS measurements with a time resolution of 0.1 s. Pt L₃-edge XANES spectra showed that CO was irreversibly adsorbed on the Pt site with structural isomerization to the chalice-motif structure in solid form. Meanwhile, H₂ was reversibly adsorbed/desorbed on Pt without a structural change. The adsorption rate of H₂ (<0.5 s) on Pt in **PtAu8-PMo12** was faster than that of CO (~ 2.5 s), whereas the interaction of Pt–H₂ was weaker than that of Pt–CO. The void analysis revealed that **PtAu8-PMo12** with CsCl-type crystal packing has two types of closed voids with a large void, V_L, being in the *ab*-plane and **PtAu8** being surrounded by four V_L, and a small void, V_S, being located over the Pt atom in **PtAu8**. H₂/CO could diffuse between the closed voids through the narrow channels

(1.6 – 2.2 Å) of **PtAu8-PMo12** and is adsorbed on Pt from the V_S space. Because the kinetic diameter of H₂ (2.89 Å) is smaller than that of CO (3.76 Å), H₂ diffuses in the narrow channel more easily than CO. In addition, CO needs to push the ligands aside to create space for adsorption on Pt. From these results, we concluded that the molecular adsorption rate is governed by the diffusion process of molecules in **PtAu8-PMo12**. Therefore, the smaller molecule, H₂, shows more rapid adsorption on Pt in **PtAu8-PMo12** compared with CO.

Experimental

Chemicals

All reagents used in this study were commercially available. Hydrogen tetrachloroaurate(III) tetrahydrate (HAuCl₄·4H₂O, 99.0%) was purchased from Kanto Chemical Co., Inc. Tetrabutyl ammonium bromide {TBABr: [N(C₄H₉)₄]Br, >98.0%}, triethylamine [TEA: N(C₂H₅)₃, >99.0%], and tetrakis (triphenylphosphine)platinum(0) [Pt(PPh₃)₄, >97.0%] were purchased from Tokyo Chemical Industry Co., Ltd. Sodium borohydride (NaBH₄, 95.0%), triphenylphosphine (PPh₃, 97.0%), phosphomolybdic acid hydrate {H₃[PMo₁₂O₄₀]·nH₂O, >95.0%}, and acetic anhydride [(CH₃CO)₂O, >97.0%] were purchased from Wako Pure Chemical Industry.

Synthesis of [Au₉(PPh₃)₈](NO₃)₃ (Au9-NO₃)

Undoped **Au9-NO₃** was prepared in accordance with the literature.³⁷ First, 0.6 mmol of Au(PPh₃)NO₃, synthesized by anion exchange from Au(PPh₃)Cl, was dispersed in 24 mL of ethanol. 0.2 mmol of NaBH₄ dissolved in 14 mL of ethanol solution was added to this suspension dropwise. After stirring at room temperature for 2 h, the brown solution was filtered through a membrane filter (pore size = 0.20 µm). The filtrate was evaporated to dryness and redissolved in dichloromethane (5 mL). The solution was filtered and dried, and the precipitate was washed with tetrahydrofuran and hexane. Finally, it was vacuum dried to produce a green powder.

Synthesis of [PtAu₈(PPh₃)₈](NO₃)₂ (PtAu8-NO₃)

PtAu8-NO₃ was synthesized in accordance with the literature.³¹ Here, 0.2 mmol of Pt(PPh₃)₃ obtained by heat treatment of Pt(PPh₃)₄²⁷ was placed in a glass container with 1.0 mmol of Au(PPh₃)NO₃. Next, 20 mL of THF was added, and a small amount of H₂ gas was bubbled while stirring at room temperature. Note that an excessive flow rate results in the formation of [PtAu₈(PPh₃)₇](NO₃)₂ as a byproduct. The red-orange precipitate was gathered by centrifugation (2500 rpm) and washed with a mixture of a small amount of dichloromethane and a large amount of diethyl ether three times. After vacuum drying, 169 mg of red-orange powder was dissolved in 10 mL of dichloromethane with 52 mg of Au(PPh₃)NO₃. Then, 0.2 mmol of TEA was added to the solution with stirring. After 24 h, this solution was evaporated and washed with diethyl ether. Finally, a brown solid was obtained after vacuum drying.

Synthesis of **TBA₃[PMo₁₂O₄₀]** (TBA-PMo12)

TBA-PMo12 was synthesized by cation exchange reaction.³⁷ Here, 0.3 mmol of H₃[PMo₁₂O₄₀]_nH₂O was dissolved in 50 mL of pure water. Next, 1.2 mmol of solid form TBABr was added to this solution. After stirring for 0.5 h at room temperature, the yellow precipitate was collected by centrifugation (3500 rpm) and washed with pure water. The precipitate was then reprecipitated using 5 mL of acetone and 45 mL of hexane. Finally, it was vacuum dried to produce yellow powder.

Synthesis of **Au9-PMo12** and **PtAu8-PMo12**

Au9-PMo12 and **PtAu8-PMo12** were synthesized in the same way as previously reported.²⁸ Here, 0.016 mmol of **TBA-PMo12** dissolved in 20 mL of acetonitrile was added at room temperature to 0.010 mmol of **Au9-NO₃**/**PtAu8-NO₃** solution (40 mL of acetonitrile). After 30 min of stirring, the precipitate was collected by centrifugation (2500 rpm) and washed with acetonitrile three times. Finally, it was vacuum-dried to give **Au9-PMo12** and **PtAu8-PMo12** solids.

Characterizations

The synthesized ligand-protected metal clusters, polyoxometalates, and their composites were analyzed by ultraviolet-visible (UV-Vis) spectroscopy, electrospray ionization (ESI) mass spectrometry, and powder X-ray diffraction (XRD). The UV-Vis spectra of **PtAu8-NO₃** and **Au9-NO₃** in methanol and ethanol solutions of CO-adsorbed **PtAu8**, which were synthesized by reacting CO with **PtAu8-NO₃** in ethanol, were measured in transmittance mode (V-770; Jasco). The UV-Vis spectra of the solid states of **PtAu8-PMo12**, **Au9-PMo12**, and CO-adsorbed **PtAu8-PMo12** were recorded using an integrating sphere unit in diffuse reflectance (DR) mode. The ESI mass spectra of **PtAu8-NO₃** and **Au9-NO₃** in acetonitrile were measured in positive-ion mode using a time-of-flight mass spectrometer (microTOF-II; Bruker). The powder XRD patterns of the composite metal clusters were determined using a powder X-ray diffractometer with Cu K α radiation (MiniFlex600; Rigaku).

The XAFS spectra of **PtAu8-PMo12** and **Au9-PMo12** were measured at the BL01B1 beamline of the SPring-8 facility operated by the Japan Synchrotron Radiation Research Institute. Si (111) double-crystal monochromators were employed to obtain the incident X-ray beam for Pt L₃- and Au L₃-edge XAFS measurements. All solid cluster samples were mixed with boron nitride as a diluent using an agate mortar. These mixtures were pressed into pellets. For Pt L₃- and Au L₃-edge XAFS measurements at 10 K, the pellets were mounted in a copper holder attached to a cryostat. To investigate the molecular adsorption behavior, quick-scan XAFS measurements (QXAFS) under transmission mode were performed at the BL36XU beamline of SPring-8 with a time resolution of 100 ms.³⁸ A Si (220) channel-cut crystal monochromator was used to obtain the incident X-rays. Pt L₃- and Au L₃-edge *in situ* XAFS measurements were carried out using the pelletized samples mounted on an *in situ* cell connected to a gas-introducing apparatus (Fig. S15†). Approximately 15 mg solid cluster

samples were mixed with 50 mg of boron nitride and pressed into φ 7 pellet. To maintain gas diffusion in the solid cluster samples, the pellets were crushed into granules and re-pelletized. For gas adsorption tests, 100% H₂ and CO were used, and sufficient amounts of gas were introduced to match the quantity of clusters present. After the sample was evacuated, 100% H₂ or 100% CO was introduced immediately using a gas valve. The XAFS data were analyzed using the xTunes software³⁹ for both X-ray absorption near-edge structure (XANES) and extended X-ray absorption fine structure (EXAFS). The k^3 -weighted χ spectra (EXAFS spectra) in the k ranges of 3.0–9.0 Å⁻¹ for the Pt L₃-edge and 3.0–18.0 Å⁻¹ for the Au L₃-edge were Fourier transformed into r space (FT-EXAFS). The curve fitting analysis was conducted using FT-EXAFS spectra in the r range of 1.8–3.2 Å for the Pt L₃-edge and 1.65–2.95 Å for the Au L₃-edge.

Computational method

Density functional theory (DFT) calculations were conducted using the Gaussian 16 program.⁴⁰ The geometries and electronic energies of **PtAu8**, and CO-, H₂-, and H (hydride)-adsorbed **PtAu8** (abbreviated as **CO-PtAu8**, **H₂-PtAu8**, and **H-PtAu8**, respectively) were calculated using the B3LYP functional. LanL2DZ basis set was used for Au and Pt atoms and 6-31G* basis set was used for C, H, O, and P atoms. Frequency analyses were performed for **PtAu8**, **CO-PtAu8** and **H₂-PtAu8** to confirm that no imaginary frequencies were obtained at the optimized geometries. The optical properties of **CO-PtAu8** were also calculated by applying the time-dependent (TD) DFT method, solving 200 states, with the same functional and basis sets used in the ground state calculations. H₂/CO adsorption energies were obtained in the difference of Gibbs free energies between H₂/CO + **PtAu8** and H₂/CO-**PtAu8** where the electronic energies were replaced by calculations using B3LYP-D3 functional with the same basis sets to incorporate dispersion interactions.

Pt L₃-edge XANES calculations were performed with the Full Potential Multiple Scattering (FPMS) code⁴¹ that employed the scattering potential without spherical potential approximation (Muffin-tin approximation). This code is based on Multiple-Scattering theory, which uses a multi-center expansion in spherical harmonics and a numerical solution of the local Schrödinger equation on each atomic site. In the overall calculation, l_{\max} is set at 8. H atoms bonded to the C atoms of the protecting ligands were not considered in the calculations because their contributions to the calculated XANES spectrum are negligible due to their long distance to the absorbing Pt atom (more than 4 Å) and their small scattering power. However, closer H atoms, as in the case of adsorption, were considered and demonstrated an effect on the spectra. Energy-dependent complex Hedin-Lundqvist potential^{42,43} was used as the optical potential.

Author contributions

S. Y. guided the whole experiment and conceived the idea. T. M. and S. K. drafted the manuscript. T. M. and

T. S. conducted the experiments, Y. O. developed analytical software for XAFS. U. S. carried out void analysis. S. K., J. O., and K. K. designed *in situ* cell for QXAFS. K. Hi., T. K. and T. U. designed the optical setup including measurement system for *in situ* QXAFS apparatus in SPring-8. K. N. gave some advice for structural analysis using low-temperature XAFS. K. Ha., Ka. Yo. and A. H. carried out XANES simulation. N. N. conducted energy calculation of clusters and gave some advice for DFT calculation results. K. S., Ke. Yo., K. Ya., and H. K. supported *in situ* XAFS measurements and discussed molecular diffusion. All the authors contributed to the final polishing of the manuscript.

Data availability

The data supporting this manuscript is available in the ESI† and are available on request. Crystallographic data for **PtAu8-PtMo12** has been deposited at the CCDC 2087794.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This study was financially supported by NEDO (JPNP14004), JSPS KAKENHI (No. 22K14543, 24K01259, 24K17562, 24H02210, 24H02211, and 24H02217), Tokyo Metropolitan Government Advanced Research (R3-1), Tokyo Human Resources Fund for City Diplomacy, and Tokyo Metropolitan University Research Fund for Young Scientists. The synchrotron radiation experiment was performed in SPring-8 under the approval of the Japan Synchrotron Radiation Research Institute (JASRI) as 202407, 2023A1326, 2022B1259, 2021B1380.

References

- 1 E. L. Albright, T. I. Levchenko, V. K. Kulkarni, A. I. Sullivan, J. F. DeJesus, S. Malola, S. Takano, M. Nambo, K. Stamplecoskie, H. Häkkinen, T. Tsukuda and C. M. Crudden, *J. Am. Chem. Soc.*, 2024, **146**, 5759–5780.
- 2 S. Li, N.-N. Li, X.-Y. Dong, S.-Q. Zang and T. C. W. Mak, *Chem. Rev.*, 2024, **124**, 7262–7378.
- 3 Y. Horita, M. Ishimi and Y. Negishi, *Sci. Technol. Adv. Mater.*, 2023, **24**, 2203832.
- 4 R. Jin, G. Li, S. Sharma, Y. Li and X. Du, *Chem. Rev.*, 2021, **121**, 567–648.
- 5 K. J. Taylor, C. L. Pettiette-Hall, O. Cheshnovsky and R. E. Smalley, *J. Chem. Phys.*, 1992, **96**, 3319–3329.
- 6 B. E. Salisbury, W. T. Wallace and R. L. Whetten, *Chem. Phys.*, 2000, **262**, 131–141.
- 7 R. H. Adnan, J. M. L. Madridejos, A. S. Alotabi, G. F. Metha and G. G. Andersson, *Adv. Sci.*, 2022, **9**, 2105692.
- 8 S. Hossain, D. Hirayama, A. Ikeda, M. Ishimi, S. Funaki, A. Samanta, T. Kawakami and Y. Negishi, *Aggregate*, 2023, **4**, e255.
- 9 M.-M. Zhang, X.-Y. Dong, Y.-J. Wang, S.-Q. Zang and T. C. W. Mak, *Coord. Chem. Rev.*, 2022, **453**, 214315.
- 10 C. A. Smith, M. R. Narouz, P. A. Lummis, I. Singh, A. Nazemi, C.-H. Li and C. M. Crudden, *Chem. Rev.*, 2019, **119**, 4986–5056.
- 11 J. Olesiak-Banska, M. Waszkielewiecz, P. Obstarczyk and M. Samoc, *Chem. Soc. Rev.*, 2019, **48**, 4087–4117.
- 12 Y. Shichibu and K. Konishi, *ChemNanoMat*, 2022, **8**, e202200194.
- 13 Z. Liu, L. Luo and R. Jin, *Adv. Mater.*, 2024, **36**, 2309073.
- 14 J. Foxley and K. L. Knappenberger Jr, *Annu. Rev. Phys. Chem.*, 2023, **74**, 53–72.
- 15 K. Kwak and D. Lee, *Acc. Chem. Res.*, 2019, **52**, 12–22.
- 16 L. Wang, J. Peng, Z. Tang, X. Kang, M. Fu and S. Chen, *Appl. Catal.*, 2018, **557**, 1–6.
- 17 Y. Zhu, H. Qian, M. Zhu and R. Jin, *Adv. Mater.*, 2010, **22**, 1915–1920.
- 18 X. Cai, G. Saranya, K. Shen, M. Chen, R. Si, W. Ding and Y. Zhu, *Angew. Chem., Int. Ed.*, 2019, **58**, 9964–9968.
- 19 K. Kwak, W. Choi, Q. Tang, M. Kim, Y. Lee, D.-E. Jiang and D. Lee, *Nat. Commun.*, 2017, **8**, 14723.
- 20 S. Takano, H. Hirai, T. Nakashima, T. Iwasa, T. Taketsugu and T. Tsukuda, *J. Am. Chem. Soc.*, 2021, **143**, 10560–10564.
- 21 H. Hirai, S. Takano, T. Nakashima, T. Iwasa, T. Taketsugu and T. Tsukuda, *Angew. Chem., Int. Ed.*, 2022, **61**, e202207290.
- 22 M. Schulz-Dobrick and M. Jansen, *Eur. J. Inorg. Chem.*, 2006, **2006**, 4498–4502.
- 23 M. A. Aubart and L. H. Pignolet, *J. Am. Chem. Soc.*, 1992, **114**, 7901–7903.
- 24 R. P. F. Kanders, P. P. J. Schlebos, J. J. Bour, W. P. Bosman, H. J. Behm and J. J. Steggerda, *Inorg. Chem.*, 1988, **27**, 4034–4037.
- 25 D. A. Krogstad, W. V. Konze and L. H. Pignolet, *Inorg. Chem.*, 1996, **35**, 6763–6771.
- 26 L. N. Ito, J. D. Sweet, A. M. Mueting, L. H. Pignolet, M. F. J. Schoonberg and J. J. Steggerda, *Inorg. Chem.*, 1989, **28**, 3696–3701.
- 27 T. Matsuyama, S. Kikkawa, Y. Fujiki, M. Tsukada, H. Takaya, N. Yasuda, K. Nitta, N. Nakatani, Y. Negishi and S. Yamazoe, *J. Chem. Phys.*, 2021, **155**, 044307–044314.
- 28 Y. Fujiki, T. Matsuyama, S. Kikkawa, J. Hirayama, H. Takaya, N. Nakatani, N. Yasuda, K. Nitta, Y. Negishi and S. Yamazoe, *Commun. Chem.*, 2023, **6**, 129.
- 29 C. F. Macrae, I. Sovago, S. J. Cottrell, P. T. A. Galek, P. McCabe, E. Pidcock, M. Platings, G. P. Shields, J. S. Stevens, M. Towler and P. A. Wood, *J. Appl. Crystallogr.*, 2020, **53**, 226–235.
- 30 S. N. Reifsnyder, M. M. Otten, D. E. Sayers and H. H. Lamb, *J. Phys. Chem. B*, 1997, **101**, 4972–4977.
- 31 J. J. Bour, R. P. F. Kanders, P. P. J. Schlebos, W. P. Bosman, H. Behm, P. T. Beurskens and J. J. Steggerda, *Recl. Trav. Chim. Pays-Bas*, 1987, **106**, 157–158.

- 32 P. Glatzel, J. Singh, K. O. Kvashnina and J. A. van Bokhoven, *J. Am. Chem. Soc.*, 2010, **132**, 2555–2557.
- 33 N. Mehio, S. Dai and D.-E. Jiang, *J. Phys. Chem. A*, 2014, **118**, 1150–1154.
- 34 S. Seino, R. Kawahara, Y. Ogasawara, N. Mizuno and S. Uchida, *Angew. Chem., Int. Ed.*, 2016, **55**, 3987–3991.
- 35 S. M. Perera, S. R. Hettiarachchi and J. W. Hewage, *ACS Omega*, 2022, **7**, 2316–2330.
- 36 J. J. Bour, P. P. J. Schlebos, R. P. F. Kanter, M. F. J. Schoondergang, H. Addens, A. Overweg and J. J. Steggerda, *Inorg. Chim. Acta*, 1991, **181**, 195–200.
- 37 T. Matsuyama, J. Hirayama, Y. Fujiki, S. Kikkawa, W. Kurashige, H. Asakura, N. Kawamura, Y. Negishi, N. Nakatani, K. Hatada, F. Ota and S. Yamazoe, *J. Phys. Chem. C*, 2021, **125**, 3143–3149.
- 38 T. Uruga, M. Tada, O. Sekizawa, Y. Takagi, T. Yokoyama and Y. Iwasawa, *Chem. Rec.*, 2019, **19**, 1444–1456.
- 39 H. Asakura, S. Yamazoe, T. Misumi, A. Fujita, T. Tsukuda and T. Tanaka, *Radiat. Phys. Chem.*, 2020, **175**, 108270–108273.
- 40 M. J. Frisch, G. W. Trucks, H. B. Schlegel, G. E. Scuseria, M. A. Robb, J. R. Cheeseman, G. Scalmani, V. Barone, G. A. Petersson, H. Nakatsuji, X. Li, M. Caricato, A. V. Marenich, J. Bloino, B. G. Janesko, R. Gomperts, B. Mennucci, H. P. Hratchian, J. V. Ortiz, A. F. Izmaylov, J. L. Sonnenberg, D. Williams-Young, F. Ding, F. Lipparini, F. Egidi, J. Goings, B. Peng, A. Petrone, T. Henderson, D. Ranasinghe, V. G. Zakrzewski, J. Gao, N. Rega, G. Zheng, W. Liang, M. Hada, M. Ehara, K. Toyota, R. Fukuda, J. Hasegawa, M. Ishida, T. Nakajima, Y. Honda, O. Kitao, H. Nakai, T. Vreven, K. Throssell, J. A. Montgomery Jr., J. E. Peralta, F. Ogliaro, M. J. Bearpark, J. J. Heyd, E. N. Brothers, K. N. Kudin, V. N. Staroverov, T. A. Keith, R. Kobayashi, J. Normand, K. Raghavachari, A. P. Rendell, J. C. Burant, S. S. Iyengar, J. Tomasi, M. Cossi, J. M. Millam, M. Klene, C. Adamo, R. Cammi, J. W. Ochterski, R. L. Martin, K. Morokuma, O. Farkas, J. B. Foresman and D. J. Fox, *Gaussian 16, Revision B.01*, Gaussian, Inc., Wallingford CT, 2016.
- 41 K. Hatada, K. Hayakawa, M. Benfatto and C. R. Natoli, *J. Phys.: Condens. Matter*, 2010, **22**, 185501.
- 42 L. Hedin and S. Lundqvist, *Solid State Phys.*, 1970, **23**, 1–181.
- 43 L. Hedin and B. I. Lundqvist, *J. Phys. C: Solid State Phys.*, 1971, **4**, 2064.