


PolyDODT: A Macrocyclic Elastomer with Unusual Properties

Journal:	<i>Polymer Chemistry</i>
Manuscript ID	PY-ART-10-2021-001426.R1
Article Type:	Paper
Date Submitted by the Author:	21-Dec-2021
Complete List of Authors:	<p>Molnár, Kristóf; The Ohio State University College of Food Agricultural and Environmental Sciences, Department of Food, Agricultural and Biological Engineering</p> <p>Kim, Hojin; California Institute of Technology, Division of Chemistry and Chemical Engineering</p> <p>Chen, Dongjie; Texas Tech University, Department of Chemical Engineering</p> <p>Helfer, Carin A.; The Ohio State University College of Food Agricultural and Environmental Sciences, Department of Food, Agricultural and Biological Engineering</p> <p>Kaszas, Gabor; The Ohio State University College of Food Agricultural and Environmental Sciences, Department of Food, Agricultural and Biological Engineering</p> <p>McKenna, Gregory B.; North Carolina State University College of Engineering, Department of Chemical and Biomolecular Engineering; Texas Tech University, Department of Chemical Engineering</p> <p>Kornfield, Julia; California Institute of Technology, Division of Chemistry and Chemical Engineering</p> <p>Yuan, Chunhua; The Ohio State University, Campus Chemical Instrument Center</p> <p>Puskas, Judit; The Ohio State University, Department of Food, Agricultural and Biological Engineering</p>

ARTICLE

PolyDODT: A Macrocyclic Elastomer with Unusual Properties

Kristof Molnar,^a Hojin Kim,^b Dongjie Chen,^c Carin A. Helfer,^a Gabor Kaszas,^a Gregory B. McKenna,^{c,d} Julia A. Kornfield,^b Chunhua Yuan,^e Judit E. Puskas*^a

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

The effect of reaction conditions on the structure of poly(3,6-dioxa-1,8-octanedithiol) (polyDODT) made by Reversible Radical Recombination Polymerization (R3P) using triethylamine (TEA), H₂O₂ and air was investigated. 800 MHz (1 and 2D) NMR was used to investigate polymer structures. Sensitivity analysis provided direct evidence for high purity cyclic polyDODT up to M_n ~ 100,000 g/mol. Comparative analysis by High Resolution Multidetector Size Exclusion Chromatography (SEC) using integrated data showed that the cycles had lower viscosity and were more compact (both for R_g and R_h) than linear samples of similar molecular weight. However, differential data revealed unusual behavior. While lower molecular weight cyclic polymers eluted later and had lower intrinsic viscosity than their linear counterparts at the same molecular weight, at higher molecular weights the polymers showed strange behavior: both the diffusion coefficient measured by Quasielastic Light Scattering (QELS) and Mark-Houwink-Sakurada plots of intrinsic viscosity for linear and cyclic polyDODT were found to converge. R3P, an aqueous based “green” method is capable of producing polymers at the 10–100 g scale in the lab, which will allow more detailed studies of this new class of biodegradable elastomers so further experimentation can be performed to elucidate the reasons for the unusual findings.

INTRODUCTION

Polymer macrocycles remain of great fundamental and practical interest, but their synthesis and characterization remain a challenge, especially at high molecular weights. Specifically, small sample size and limits in the detection of linear contaminants in macrocycles hinder the investigation of the dynamics of cyclic polymers, particularly highly entangled ones. Also, most examples in the literature are for polymers with T_g above room temperature, and we found relatively little data for elastomers.^{1–3}

In 2012, we reported the synthesis and initial characterization of disulfide polymers obtained by oxidation of 2-[2-(2-sulfanylethoxy)ethoxy]ethanethiol (DODT) using a system comprised of air, dilute hydrogen peroxide and triethylamine (TEA) as a catalyst that can be recycled.^{4–6} High molecular weight disulfide polymers (up to M_n = 250,000 g/mol) with polydispersity indices as low as M_w/M_n = 1.15 were obtained in this two-phase system (with a TEA/monomer organic phase and

aqueous reaction mixture). The product is a transparent elastomer (T_g of –50 °C) that can be depolymerized back to the original monomeric units using dithiothreitol (DTT) in 33 h. Up to the highest molecular weights amenable to analysis using MALDI-ToF (up to M_n ~ 3,000 g/mol), the products were pure cyclic polymers. Based on these findings, we proposed a mechanism for this unique two-phase system, and coined the term “Reversible Radical Recombination Polymerization” (R3P, Figure 1).^{7,8} The first step is proton abstraction from the dithiol by TEA; then the dianions dissolve into the aqueous phase where H₂O₂ oxidizes them into diradicals, which can recombine into cyclic structures or react with a proton to be end-capped to form linear polymers with thiol end groups. Small cyclic species can reenter the organic phase, as was shown by NMR, where they may be ring-opened by a dithiol monomer. However, we found that the polymerization is extremely fast and high molecular weight polymers rapidly precipitate in the water phase. Despite its exothermic character, the process easily scales to 10–100 g batches of polyDODT in the lab. The recovered precipitates were shown to be either cyclic or a mixture of cyclic and linear polymers, depending on the reaction conditions (see Figure 1).^{7,8} Recovered polymers could be chain-extended readily with ethylene-dithiol (ED) or could be further oxidized into larger polymers, to M_n ~ 400,000 g/mol. According to the proposed mechanism, a minimum of two molar equivalent of TEA is needed to form the dianion, and excess H₂O₂ is needed for effective oxidation. Scouting experiments showed that less than 2/1 TEA/DODT and H₂O₂/DODT yielded low molecular weight, predominantly linear oligomers (M_n < 3,000 g/mol) with traces (< 1%) of cyclic structures.⁹

^a The Ohio State University, College of Food, Agricultural, and Environmental Sciences, Department of Food, Agricultural and Biological Engineering, 220 FABE, 1680 Madison Avenue, Wooster, OH 44691

^b California Institute of Technology, Division of Chemistry and Chemical Engineering, Pasadena, CA 91125

^c Texas Tech University, Department of Chemical Engineering, Lubbock, TX 79409-3121

^d The Ohio State University, Campus Chemical Instrument Center, 496 W 12th Ave, Columbus, OH 43210

^e North Carolina State University, Department of Chemical and Biomolecular Engineering, Raleigh, NC 27695-7905

† Footnotes relating to the title and/or authors should appear here.

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x

We extended R3P to thiol-functionalized polyisobutylene (HS-PIB-SH) to produce PIB-disulfide elastomers up to $M_n \sim 100,000$ g/mol.¹⁰ 750 MHz correlation NMR demonstrated the formation of a high purity macrocycle with $M_n = 25,000$ g/mol. A sample with $M_n \sim 125,000$ g/mol, believed to be cyclic, was analyzed by five-detector SEC and compared to linear PIB standards. The putative cyclic polymer had lower intrinsic viscosity but, surprisingly, larger R_g and R_h than linear PIBs at the same molecular weight. This PIB-disulfide had higher T_g than a linear PIB standard (-63 vs -73 °C), an additional evidence for cyclic structure based on some reports^{11–13}, but others reported similar T_g .¹⁴ However, end group quantification by NMR at this molecular weight may be challenged.

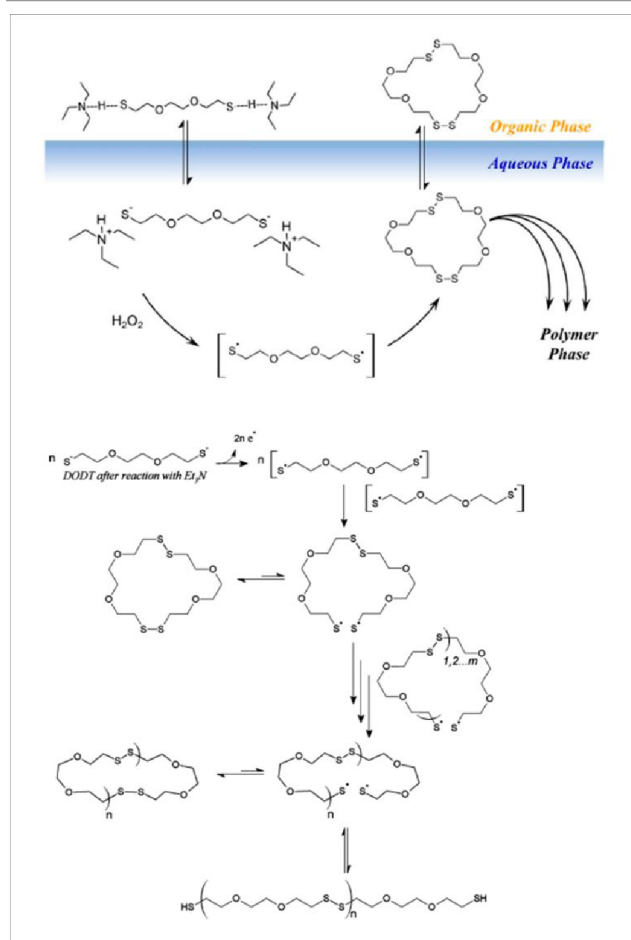


Figure 1. Proposed mechanism of R3P of DODT. The organic phase is TEA/monomer, a clear oily liquid. Reproduced with permission from.⁹

The cationic macrocyclization of polyphthalaldehyde (PPA) reported in 2013¹⁵, which also provides chain extension or contraction and produces cyclic structures such as our DODT- and PIB-based R3P systems, uses a backbone for which depolymerization is favored at room temperature (PPA ceiling temperature -40 °C) and is prevented by either cyclization or “end capping.” Since residual linear PPA is expected to spontaneously depolymerize, very pure cycles could be obtained. Using triple-detection SEC, a cyclic PPA with $M_n =$

11,700 g/mol was compared to a linear counterpart made by anionic polymerization and end-capped to prevent depolymerization. The cyclic PPA eluted later than the linear PPA and had lower intrinsic viscosity. Elution time and viscosity plots were not shown for higher molecular weight samples. The highest M_n reported for the cationic PPA system was 100,000 g/mol, claimed to have cyclic structure based on the chemistry of the system, but no direct evidence was provided. Cyclic structures with higher molecular weights (up to 600,000 g/mol) have been reported for PS¹⁶, polyoctanomers¹⁷ and DNA^{18,19} but comparative physico-chemical analyses have only been provided for much lower molecular weights.

Purification of cyclic polymers, mostly PS, by Liquid Chromatography at the Critical Condition (LCCC) has been reported, claiming less than 1% linear contaminants.^{20–22} However, when applied to polyDODT, we have shown that this method was not able to detect up to 6 wt% linear contaminants that were deliberately added.²³ Literature suggested that rheological investigations of high molecular weight cyclic PS purified by LCCC have yielded contradictory results because of the presence of undetected linear contaminants.^{14,24} For polyDODT, an additional challenge is that linear samples with $M_n > 3,000$ g/mol have not been available for comparative studies until now. This paper will discuss the effect of reaction conditions on the structure of polyDODTs, and a comparative analysis of cyclic and linear polyDODTs using Five-detector High Resolution Size Exclusion Chromatography.

EXPERIMENTAL

MATERIALS

3,6-dioxa-1,8-octanedithiol (DODT) 95% (Aldrich), triethylamine (TEA) (TCI), H₂O₂ 30 wt% (Sigma-Aldrich), acetone technical grade (Sigma), tetrahydrofuran (THF) HPLC grade non-stabilized (Fischer Scientific), methanol (MeOH) HPLC grade (Fischer Scientific), mercaptoethanol (SH-Et-OH, Sigma), deuterated chloroform (CDCl₃, Chemical Isotope Laboratories, 99.8%) were used as received.

Synthesis of polyDODTs

End-capping with mercaptoethanol. DODT, TEA and SH-Et-OH were mixed for 30 minutes in a 100 mL beaker with a magnetic stir bar at 200 rpm. Five samples were prepared as shown in Table 1. The TEA: -SH ratio was kept at 1:1. 6.5 mL 30 wt% (57.35 mmol) H₂O₂ was added to the mixture using a KD Scientific K100 syringe pump at a rate of 8.4 mL/h, with mixing increased to 400 rpm and compressed air bubbled into the mixture. After all the peroxide was added, the mixture was stirred for 2 h at a rate of 200 rpm. A photo of the setup can be seen in Figure S1 A. The supernatant was decanted, and the product was washed 3 times for 30 minutes with distilled water and 3 times for 30 minutes with methanol. Then the polymer was dried under vacuum until constant weight. Samples are denoted MX where X is the DODT/SH-Et-OH molar ratio.

Table 1 R3P polymerization of 27.5 mmol DODT in the presence of SH-Et-OH

Sample ID	TEA (mmol)	Mercaptoethanol (mmol)
M1	123.4	54.96
M10	86.2	5.50
M25	83.9	2.20
M50	83.3	1.10
M100	82.8	0.55

Polymerizations under Varying Reaction Conditions.

Polymerizations were carried out by varying reaction conditions as described in Table 2.

Table 2 Polymerization conditions

Method	Sample ID	Peroxide %	Reaction	Air bubbling
1	1.1.; 1.2.; 1.3.	3	Pump H ₂ O ₂ into DODT/TEA	No
2	2.1.; 2.2.; 2.3.	30	Dump DODT/TEA into H ₂ O ₂	No
3*	3.1.*	30	Pump DODT/TEA into H ₂ O ₂	No
4	4.1.	30	Drip H ₂ O ₂ into DODT/TEA	Yes

DODT:TEA:H₂O₂ = 27.5:82.2:57.3; * DODT:TEA:H₂O₂ = 32:73:64

In general, DODT and TEA were mixed for 30 minutes in a 100 mL beaker with a magnetic stir bar at 200 rpm.

In **Method 1**, 3% aqueous H₂O₂ was added to the DODT/TEA mixture by a KD Scientific K100 syringe pump at a rate of 8.4 mL/h into the mixture, while mixing was set to 400 rpm. Three reactions were carried out. After all the peroxide was added, the mixtures were stirred for 2 h at a rate of 200 rpm. The supernatant layers were decanted, and the products were washed 3 times for 30 minutes with distilled water and 3 times for 30 minutes with methanol. Then the polymers were dried under vacuum until constant weight.

In **Method 2**, DODT/TEA mixtures were dumped into 30% aqueous H₂O₂. Three reactions were performed for 1, 2 and 5 minutes and stopped by pouring the mixtures into 400 mL chilled methanol. The resulting milky samples were centrifuged for 30 minutes (4,000 rpm with 7 minutes ramping up and 5 minutes ramping down) then the supernatant layers were decanted. The polymers were washed with methanol and centrifuged 2 more times. Then the polymers were dissolved in 15 mL chloroform to separate water residues and dried under the hood under vacuum until constant weight.

In **Method 3**, the DODT/TEA mixture was added into 30 wt% aqueous H₂O₂ by a KD Scientific K100 syringe pump at a rate of 20 mL/h. After the addition of the DODT/TEA mixture, the supernatant was decanted, and the white creamy product was washed 3 times for 30 minutes with 50 mL acetone and dried under vacuum until constant weight.

In **Method 4**, 30 wt% peroxide was dripped into the DODT/TEA mixture manually for 45 minutes, with compressed air bubbled

through a glass pipette submerged into the reaction mixture. The volume rate of compressed air was several bubbles per second without foaming up the reaction. After all the peroxide was added, the reaction flask was closed, and the mixture was stirred for 2 h. Then supernatant was decanted, and the product was washed 2 times for 30 minutes with distilled water and 3 times for 30 minutes with acetone. Then the polymer was dried under vacuum until constant weight.

Synthesis of High Molecular Weight PolyDODTs

The synthesis method was very similar to Method 4 but after completion of the peroxide addition the mixtures were stirred for 2 h in an open flask, and the polymers were washed with methanol instead of acetone before drying under vacuum to constant weight.

Proton and Carbon Nuclear Magnetic Resonance Spectroscopy (¹H and ¹³C NMR)

¹H NMR spectra were recorded on Bruker 400, 700 or 800 MHz NMRs using deuterated chloroform (CDCl₃) as solvent. The resonance of non-deuterated chloroform at $\delta=7.27$ ppm was used as internal reference. The number of scans was 128, with a relaxation time of 10 second. Data was collected at 298 K. For the sensitivity analysis, a linear polyDODT was mixed with a cyclic polyDODT and data was collected at 288 K using the 800 MHz NMR equipped with a 5 mm Triple-resonance Inverse (TXI) cryoprobe with Z-Gradients. ¹³C NMR was collected with 2048 scans and 10 s relaxation at 298 K on the Bruker 700 MHz NMR (more sensitive for carbon than the 800 MHz instrument) using a 5 mm Triple-resonance Observe (TXO) cryoprobe with Z-Gradients. 2D multiplicity-edited HSQC measurement with sensitivity enhancement was carried out on the Bruker 800 MHz NMR: spectral width ¹H (16ppm) and ¹³C (240ppm); data matrix 2048 X 128; number of scans: 16; relaxation delay: 1s. NMR data were processed and analyzed using TopSpin 3.6.2, and chemical shifts (¹H and ¹³C) were referenced internally against the solvent peak.

High Resolution Five-detector Size Exclusion Chromatography (SEC)

The SEC instrument consisted of an Agilent 1260 infinity isocratic pump, a Wyatt Eclipse DUALTEC separation system, an Agilent 1260 infinity variable wavelength detector (UV set at 254 nm), a Wyatt OPTILAB T-rEX interferometric refractometer (DRI), a Wyatt DAWN HELOS-II 18-angle static light scattering detector (MALS) with a built-in dynamic light scattering (QELS) module, a Wyatt Viscostar online differential viscometer and an Agilent 1260 infinity standard autosampler. 6 StyragelVR columns (HR6, HR5, HR4, HR3, HR1, and H0.5) were thermostated at 35°C. THF was the mobile phase at a flow rate of 1 mL/min, continuously distilled from CaH₂. In each case 100 μ L of 2 mg/mL polymer solution was injected. The results were analyzed using the ASTRA 6 software (Wyatt Technology). Two concentration detectors were used: DRI with $dn/dc = 0.132$ for polyDODT⁶ and UV with absorption coefficients obtained assuming 100% mass recovery. The traces overlapped exactly.

Two close to monodisperse PS standards ($M_n = 30,000$ and $100,000$ g/mol) were injected with each new series of measurements to doublecheck accuracy of the instrument.

RESULTS AND DISCUSSION

Synthesis of Linear PolyDODT by End-capping with Mercaptoethanol (SH-Et-OH).

As mentioned in the Introduction, until recently we had been able to produce only low molecular weight linear polyDODT oligomers ($M_n \sim 1,000$ - $3,000$ g/mol).²³ End-capping with SH-Et-OH provided molecular weight control with M_n directly proportional to the DODT/SH-Et-OH ratio – Figure 2 displays the excellent correlation, and Table 3 summarizes the data.

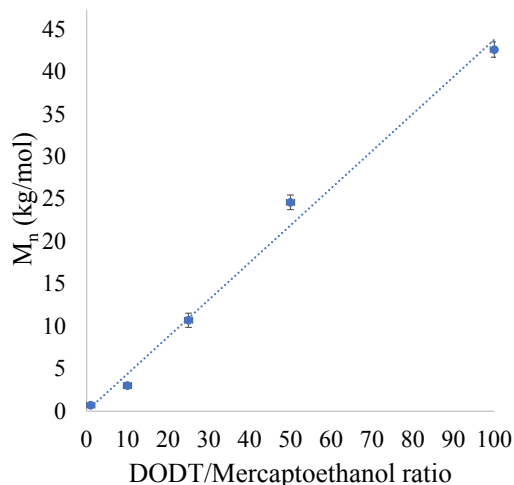


Figure 2. M_n vs DODT/SH-Et-OH ratio, $R^2 = 0.9958$. Error bars represent 95% confidence level calculated by Astra (SEC).

Table 3. Molecular weight and conversion data for the reactions in the presence of SH-Et-OH.

ID	M_n (g/mol)	M_w (g/mol)	\bar{D}	Conversion (%)
M1	700	830	1.27	62
M10	3,000	7,000	2.34	82
M25	10,700	18,600	1.74	95
M50	24,400	33,400	1.36	99
M100	42,500	59,500	1.40	84

The end groups in this case were $-\text{CH}_2-\text{CH}_2-\text{OH}$, as shown by ^1H NMR of sample M10. (Figure 3). The main chain proton signals appear at δ_{H} (400 MHz; CDCl_3) 2.98 (4 H_d , t, CH_2SSCH_2); 3.65 (4 H_f , s, $\text{OCH}_2\text{CH}_2\text{O}$); 3.75 (4 $\text{H}_{c,e}$, t, $\text{OCH}_2\text{CH}_2\text{SSCH}_2\text{CH}_2\text{O}$) ppm, while signals related to the end groups appear at 2.35 (2 H_a , br s, CH_2OH) and 3.81-3.83 (4 H_b , t, CH_2OH) ppm. This method yielded linear polyDODTs with up to $M_n \sim 40,000$ g/mol, but the NMR of the last sample had signals assigned to $-\text{SH}$ end groups so not all chain ends were capped with $-\text{OH}$ groups.

Effect of Reaction Conditions on Polymer Structure

Polymers were produced by four different methods – the results are summarized in Table 4. Method 1 and the first two samples of Method 2 yielded polymers with thiol end groups (see a picture of L1.1 in Figure S1B and the proton NMR of L2.2 in Figure S2). The M_n of the samples was calculated based on the ratio of the end group protons (SH , 1.6 ppm and CH_2SH , 2.75 ppm) relative to the main chain protons (2.98 – 3.75 ppm). Table 4 compares M_n values from SEC and NMR. There is very good agreement up to $M_n \sim 80,000$ g/mol. In case of the third sample from Method 2, the M_n calculated from NMR is higher than that from SEC, indicating that a fraction of the sample does not have thiol end groups, so this sample is a mixture of linear (~40%) and cyclic (60%) polyDODTs. A representative ^{13}C NMR is shown in Figure S3.



Table 4. Effect of reaction conditions on the R3P of DODT.

ID	M_n (SEC) (g/mol)	M_n (NMR) (g/mol)	\bar{D}	DODT conversion (%)
Method 1				
L1.1	27,800	33,800	1.95	73
L1.2	27,900	28,700*	2.18	90
L1.3	37,800	31,300*	2.21	85
Method 2				
L2.1	15,100	17,500	1.61	32
L2.2	78,000	82,900	2.05	55
L/C2.3 40/60	94,300	146,000	2.16	75
Method 3				
C3.1	35,800		2.74	54
Method 4				
C4.1	84,700		1.26	

800 MHz, except *400 MHz

The 800 MHz NMR of the polymers from Methods 3 and 4 did not show any end group signals (see the NMR of C3.1 in Figure S4). This may be an indication of cyclic structures. NMR and MALDI-MS of low molecular weight poly(DODT) ($M_n < 3000$ g/mol) also demonstrated cyclic structures.^{6,23} At ~30 nM theoretical detection limit²⁵, 800 MHz NMR would be able to detect 0.4 and 1.7% linear polyDODT with $-\text{SH}$ end groups in 45 mg cyclic samples of $M_n = 35,800$ and $84,700$ g/mol (C3.1 and C4.1 in Table 4) in the NMR tube. Thus, NMR data may be interpreted as indicating very pure cycles for C3.1 and C4.1. 2D NMR of L1.1 (Figure 4) highlights the signal correlating the carbon (24.6 ppm, ^{13}C) with the protons (2.75 ppm, ^1H) in the $-\text{CH}_2$ group next to the thiol ($-\text{C}-\text{H}_2-\text{S}-\text{H}$). No signal was found at 24.6 ppm in the ^{13}C NMR spectrum of C3.1, indicating that there were no end groups in the polymer.

ARTICLE

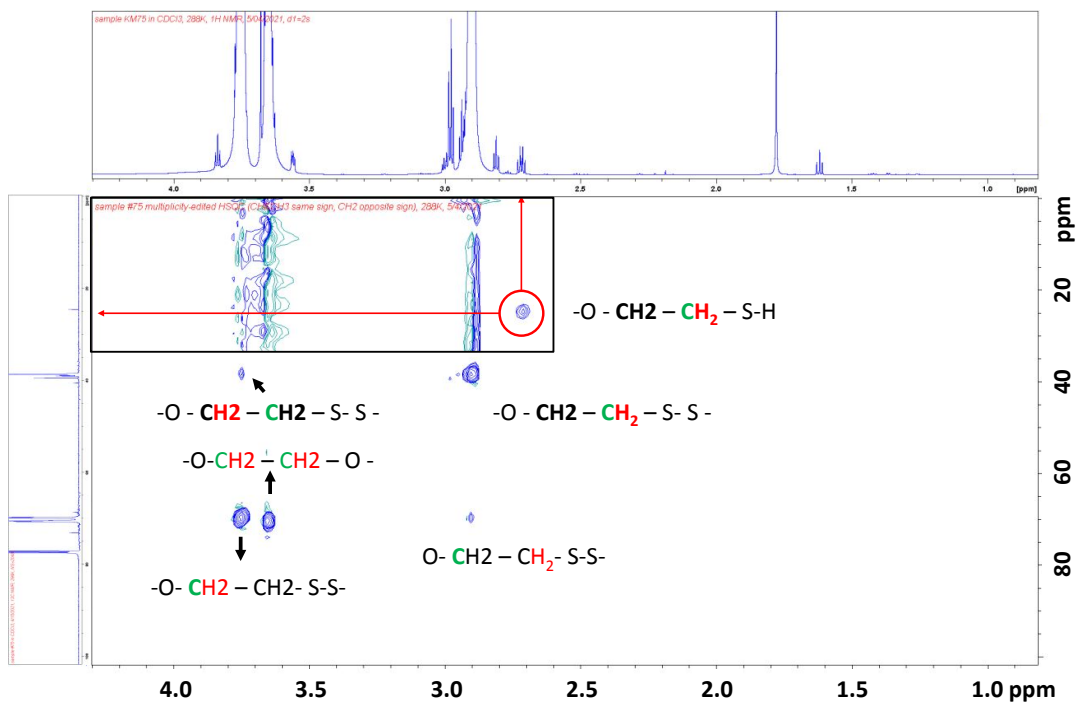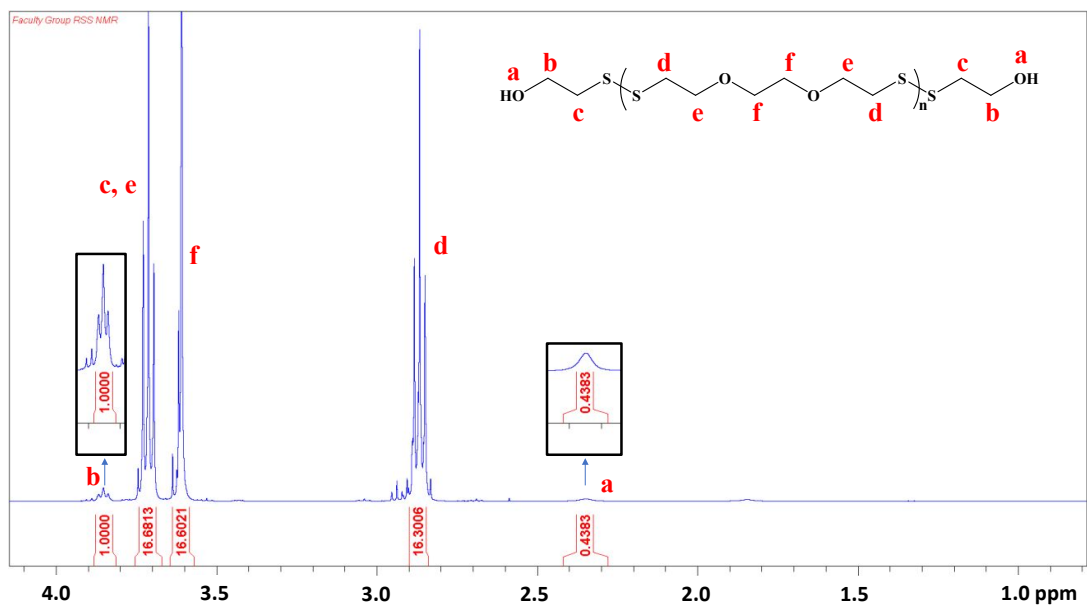

To test the sensitivity (the amount of linear chains that need to be added to be detectable) of 800 MHz NMR, 1.3 – to 17 wt% L1.1 was mixed with C3.1 and tested with the 800 MHz NMR which has the highest sensitivity for ^1H NMR measurement ($S/N = 7400$ for 0.1 % Ethylbenzene standard). Measurements were carried out at 288K to shift the broad water peak from the solvent downfield to not overlap with the -SH resonance at 1.6 ppm. Since the HS- triplet was very clean while the $-\text{CH}_2\text{-SH}$ seemed to overlap with a satellite, this integral was used to calculate $M_n = 33,800$ g/mol for L1.1 (see Table 4). Figure 5 and Table 5 summarize the data. At 29 nmol linear content, no HS-end group signals were detected. At 37 nmol a small signal appeared, and the integral indicated 1.8 wt% L1.1, in comparison with the nominal 1.3 wt% due to the linear chains that were added.

As the concentration of the linear polymer increases the -SH signal intensity increases, giving good agreement between the nominal and measured end group concentrations. C3.1 had $M_n = 35,800$ g/mol measured by SEC, which is similar to that of L1.1 (see Table 4). Therefore, based on our NMR investigation, C3.1 contains less than 1.3 wt% linear contamination, if any. This agrees well with the calculated sensitivity data.²⁵ The lack of any other signals that may be associated with end groups suggest that C3.1 is a cyclic poly(DOT).

High-resolution Size Exclusion Chromatography (SEC).

Table 6. summarizes integrated SEC data for the linear and cyclic polymers with similar molecular weights from Table 4, and Figure 6 compares the SEC traces. Cyclic samples eluted later than the linear counterparts, but the difference is smaller at higher molecular weight. This difference in time is due to the smaller hydrodynamic volumes that physically more compact cyclic polymers possess, which is consistently reported for cyclic polymers.^{26,27} The R_g and R_h values and intrinsic viscosities of the cycles are also smaller than those of the linear samples of similar molecular weight and close to the theoretical expectation of $g \approx 0.66$.^{16,28–32}

Table 5 Sample compositions and results of sensitivity analysis for ^1H NMR (800 MHz).

ID	Linear content		
	Nominal		-SH integral
	(nmol)	%	%
L1.1	2381	100.0	100.0
Mix 1	29	1.5	NA
Mix 2	37	1.3	1.8
Mix 3	63	2.0	2.0
Mix 4	124	3.9	3.8
Mix 5	250	7.7	8.6
Mix 6	473	17.0	17.9

Cyclic polymers are expected to have lower intrinsic viscosities than linear counterparts: theory suggests a ratio of $g' = [\eta_{\text{cyclic}}]/[\eta_{\text{linear}}] = 0.4 - 0.5$.^{28–31} However, this ratio has been reported experimentally to range from 0.3 – 0.9. Jeong *et al.*

carried out a thorough study on cyclic and linear PSs focusing on the dilute solution properties and measured $g' = 0.57 - 0.63$.³³ We found g' values of 0.74 and 0.65, respectively (see Table 6).

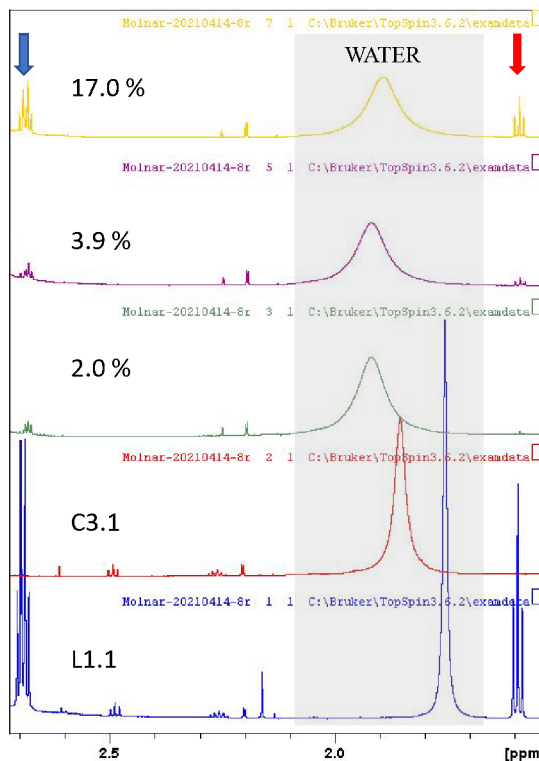


Figure 5. Sensitivity analysis for ^1H NMR (800 MHz). Broad peak to the left to the -SH 1.6 is water. Pure L1.1 (blue), pure C3.1 (red), Mix 2 (green), Mix 5 (purple), Mix 7 (yellow). Blue arrow indicates the $-\text{CH}_2\text{-SH}$ at 2.71 ppm and the red arrow indicates the -SH triplet at 1.6 ppm. Numbers indicate linear content in wt%.

To take out the influence of polydispersity, plots from individual SEC runs were constructed. Figure 7(A and B) compares M_i – retention time plots for the linear-cyclic pairs in Table 6 (L1.1 – C3.1 and L2.2- C4.1). Cyclic samples eluted later than the linear counterparts at the same molecular weight but the difference decreased with increasing molecular weight, similarly to that shown in the SEC traces in Figure 6.

Table 6. Integrated SEC data.

ID	M_n (SEC) (g/mol)	\bar{D}	R_g nm	R_h nm		Visc mL/g	g'
				Visc	QELS		
Lower MW							
L1.1	27,800	1.95	12.2	8.5	8.4	36.3	
C3.1	35,800	2.74	9.5*	5.8		26.7	0.74
Higher MW							
L2.2	78,000	2.05	21.9	15.5	15.7	86.8	
C4.1	84,700	1.26	16.1	10.9	-	56.7	0.65

Figure 8 compares the Mark-Houwink-Sakurada plots for the linear-cyclic pairs in Table 6 (L1.1 – C3.1 and L2.2- C4.1). In the lower molecular weight range, the viscosity of C3.1 is lower than that of L1.1, but with increasing molecular weights the plots converge. The 800 MHz NMR sensitivity analysis demonstrated that C3.1 had less than 1.3% linear contaminants if any. The situation is similar for L2.2 and C4.1, with less difference.

The QELS detector measures translational diffusion coefficients (D). The ratio of D of circular and linear species $C = D_c/D_l$ is predicted to be greater than unity and independent of length for long molecules, but the exact value is still debated.^{18,34} Calculations based on classical Kirkwood hydrodynamic theory predicted $C \sim 1.18$, while renormalization group calculations predicted $C \sim 1.45$. Some experiments on synthetic polymer solutions reported values of $C \sim 1.11$ – 1.2 , in reasonable agreement with the calculations using Kirkwood theory, but one reported $C \sim 1.36$, in closer agreement with the renormalization group theory calculation. We found that the $D - M_i$ plots are identical within experimental error (see Figure 9) but it must be considered that QELS is less accurate than viscometry.

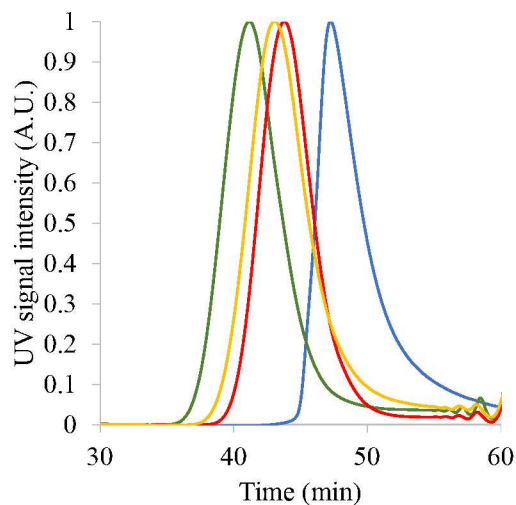


Figure 6. UV traces (A) of L1.1 (red); C3.1 (blue); L2.2 (green); C4.1 (orange) from Table 6.

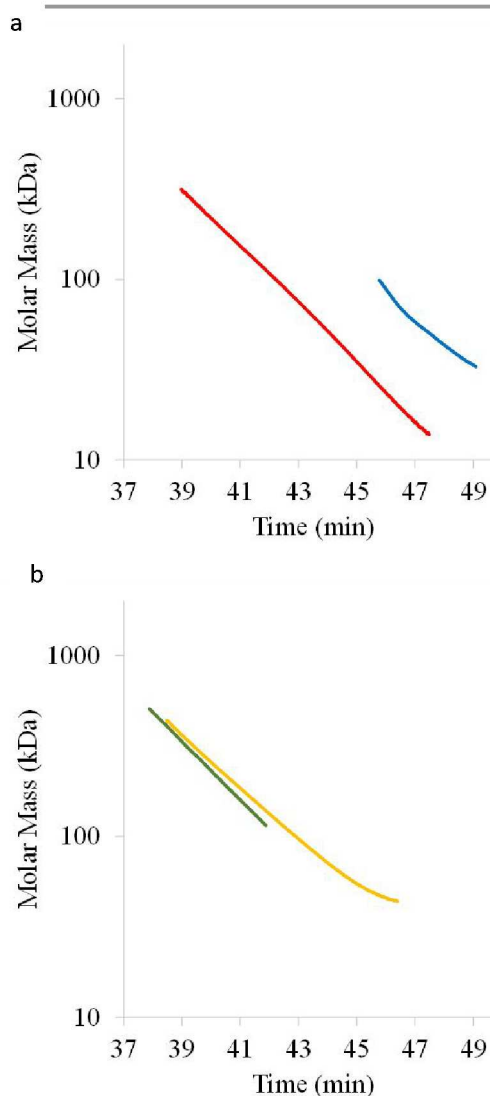


Figure 7. M_i - retention time plots for linear and cyclic polyDODTs: C3.1 – L1.1 (a) and C4.1 – L2.2 (b) from Table 6.

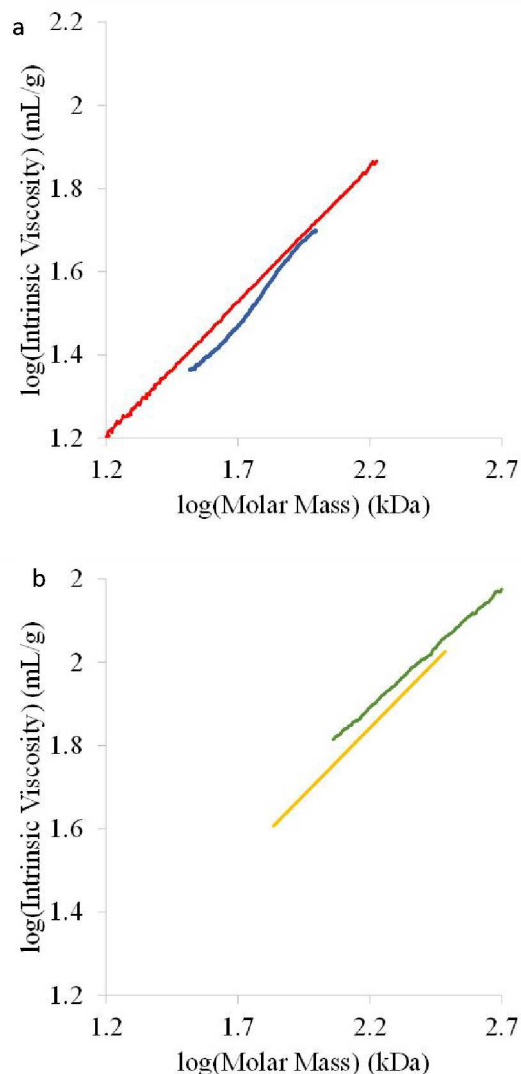


Figure 8. MHS plots of cyclic and linear polyDODTs: L1.1 (red) - C3.1 (dark blue) (a) and L2.2 (green) - C4.1 (orange) (b).

The NMR investigations indicate pure rings, not mixtures, but the dilute solution properties are contradictory, especially at higher molecular weights. We have no explanation for the strange behavior currently, but detailed investigations of these unique elastomers are in progress. One theory is the flexible nature of these elastomers. The unique capability of R3P is that it can produce high molecular weight polymers at large scale, for rheological and other studies. Table 7 gives some examples and Figure S1C shows a picture of a sample. The very high molecular weight, however, prevented detailed structural investigations so they are labeled "X". Rheological testing of the polymers is in progress and will be published separately.

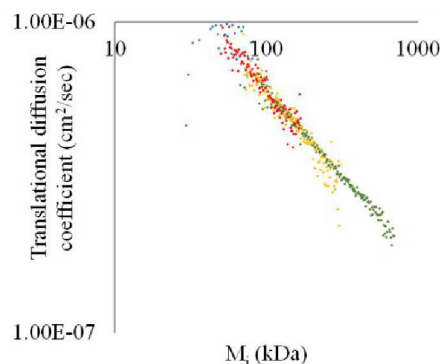


Figure 9. Diffusion coefficient vs molecular weight (M_n) for: L1.1 (red), L2.2 (green), C3.1 (dark blue) and C4.1 (orange).

Table 7. High molecular weight polyDODT samples.

ID	M_n (g/mol) SEC	M_w (g/mol) SEC	\bar{D}
X1	175,500	398,500	2.27
X2	206,700	301,900	1.46
X3	280,500	399,900	1.43
X4	300,000	417,000	1.39
X5	325,400	405,900	1.25
X6	366,700	556,000	1.52

Conclusions

In summary, we synthesized polyDODTs by R3P and characterized the polymers by NMR and High-resolution Five-detector SEC. Sensitivity analysis by 800 MHz NMR showed a detection limit of $\sim 1.3\%$ linear contaminants in a sample with $M_n = 35,800$ g/mol. PolyDODT is capable of chain extension to higher molecular weights, depolymerization to lower molecular weights, or dynamic intermixing with other polymer chains, both cyclic and linear. These properties may give great flexibility in the synthesis and characterization of pure cyclic polymers. The aqueous "green" R3P method yields polymers at the 10-100 g scale in the lab, which will allow more detailed studies into the reasons for the unusual findings at higher molecular weights.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by the U.S. Department of Energy, Office of Science, Basic Energy Sciences under Award #DE-SC0018891 and a start-up fund of The Ohio State University #11232011000-11-PUSKAS. The work at TTU and Caltech was supported by the U.S. Department of Energy, Office of Science, Basic Energy Sciences under Awards DE-SC0018657 and DE-SC0018655.

Notes and references

- 1 J. Wang, R. R. Butler, F. Wu, J.-F. Pombert, J. J. Kilbane and B. C. Stark, Enhancement of Microbial Biodesulfurization via Genetic Engineering and Adaptive Evolution, *PLoS One*, 2017, **12**, e0168833.
- 2 J. Roovers and P. M. Toporowski, Synthesis and characterization of ring polybutadienes, *J. Polym. Sci. Part B Polym. Phys.*, 1988, **26**, 1251–1259.
- 3 C. W. Bielawski, D. Benitez and R. H. Grubbs, Synthesis of Cyclic Polybutadiene via Ring-Opening Metathesis Polymerization: The Importance of Removing Trace Linear Contaminants, *J. Am. Chem. Soc.*, 2003, **125**, 8424–8425.
- 4 US 9,193,680 B2, 2013.
- 5 US 8,552,143, 2013.
- 6 E. Q. Rosenthal, J. E. Puskas and C. Wesdemiotis, Green Polymer Chemistry: Living Dithiol Polymerization via Cyclic Intermediates, *Biomacromolecules*, 2012, **13**, 154–164.
- 7 E. Q. Rosenthal-Kim and J. E. Puskas, Green polymer chemistry: Living oxidative polymerization of dithiols, *Pure Appl. Chem.*, 2012, **84**, 2121–2133.
- 8 E. Rosenthal-Kim and J. Puskas, Green Polymer Chemistry: Investigating the Mechanism of Radical Ring-Opening Redox Polymerization (R3P) of 3,6-Dioxo-1,8-octanedithiol (DODT), *Molecules*, 2015, **20**, 6504–6519.
- 9 P. Mulay, University of Akron, 2019.
- 10 J. E. Puskas and S. Sen, Synthesis of Biodegradable Polyisobutylene Disulfides by Living Reversible Recombination Radical Polymerization (R3P): Macrocycles?, *Macromolecules*, 2017, **50**, 2615–2624.
- 11 Z. Jia and M. J. Monteiro, Cyclic polymers: Methods and strategies, *J. Polym. Sci. Part A Polym. Chem.*, 2012, **50**, 2085–2097.
- 12 J. Cui, J.-X. Yang, Y.-G. Li and Y.-S. Li, Synthesis of High Performance Cyclic Olefin Polymers (COPs) with Ester Group via Ring-Opening Metathesis Polymerization, *Polymers (Basel)*, 2015, **7**, 1389–1409.
- 13 T. Yamamoto and Y. Tezuka, Topological polymer chemistry: a cyclic approach toward novel polymer properties and functions, *Polym. Chem.*, 2011, **2**, 1930.
- 14 Y. Doi, K. Matsubara, Y. Ohta, T. Nakano, D. Kawaguchi, Y. Takahashi, A. Takano and Y. Matsushita, Melt Rheology of Ring Polystyrenes with Ultrahigh Purity, *Macromolecules*, 2015, **48**, 3140–3147.
- 15 J. A. Kaitz, C. E. Diesendruck and J. S. Moore, End group characterization of poly(phthalaldehyde): Surprising discovery of a reversible, cationic macrocyclization mechanism, *J. Am. Chem. Soc.*, 2013, **135**, 12755–12761.
- 16 A. Takano, Y. Ohta, K. Masuoka, K. Matsubara, T. Nakano, A. Hieno, M. Itakura, K. Takahashi, S. Kinugasa, D. Kawaguchi, Y. Takahashi and Y. Matsushita, Radii of Gyration of Ring-Shaped Polystyrenes with High Purity in Dilute Solutions., *Macromolecules*, 2012, **45**, 369–373.
- 17 C. W. Bielawski, D. Benitez and R. H. Grubbs, An 'Endless' Route to Cyclic Polymers, *Science (80-.)*, 2002, **297**, 2041–2044.
- 18 R. M. Robertson, S. Laib and D. E. Smith, Diffusion of isolated DNA molecules: Dependence on length and topology, *Proc. Natl. Acad. Sci.*, 2006, **103**, 7310–7314.
- 19 Y. Li, K.-W. Hsiao, C. A. Brockman, D. Y. Yates, R. M. Robertson-Anderson, J. A. Kornfield, M. J. San Francisco, C. M. Schroeder and G. B. McKenna, When Ends Meet: Circular DNA Stretches Differently in Elongational Flows, *Macromolecules*, 2015, **48**, 5997–6001.
- 20 H. H. C. Lee, H. H. C. Lee, W. Lee, T. Chang and J. Hoovers, Fractionation of cyclic polystyrene from linear precursor by HPLC at the chromatographic critical condition, *Macromolecules*, 2000, **33**, 8119–8121.
- 21 D. C. Ho, K. M. Asuoka, K. K. Oguchi, T. A. Sari, D. K. Awaguchi, A. T. Akano, Y. M. Atsushita, D. Cho, K. Masuoka, K. Koguchi, T. Asari, D. Kawaguchi, A. Takano and Y. Matsushita, Preparation and Characterization of Cyclic Polystyrenes, *Polym. J.*, 2005, **37**, 506–511.
- 22 Q. Huang, J. Ahn, D. Parisi, T. Chang, O. Hassager, S. Panyukov, M. Rubinstein and D. Vlassopoulos, Unexpected Stretching of Entangled Ring Macromolecules, *Phys. Rev. Lett.*, 2019, **122**, 208001.
- 23 K. Molnar, C. A. Helfer, G. Kaszas, E. Krisch, D. Chen, G. B. McKenna, J. A. Kornfield and J. E. Puskas, Liquid chromatography at critical conditions (LCCC): Capabilities and limitations for polymer analysis, *J. Mol. Liq.*, 2021, **322**, 114956–114965.
- 24 M. Kapnistos, M. Lang, D. Vlassopoulos, W. Pyckhout-Hintzen, D. Richter, D. Cho, T. Chang and M. Rubinstein, Unexpected power-law stress relaxation of entangled ring polymers, *Nat. Mater.*, 2008, **7**, 997–1002.
- 25 Sensitivity in NMR, <https://www2.chem.wisc.edu/~cic/nmr/Guides/Other/sensitivity-NMR.pdf>.
- 26 C. D. Roland, H. Li, K. A. Abboud, K. B. Wagener and A. S. Veige, Cyclic polymers from alkynes, *Nat. Chem.*, 2016, **8**, 791–796.
- 27 Z. Miao, D. Pal, W. Niu, T. Kubo, B. S. Sumerlin and A. S. Veige, Cyclic Poly(4-methyl-1-pentene): Efficient Catalytic Synthesis of a Transparent Cyclic Polymer, *Macromolecules*, 2020, **53**, 7774–7782.
- 28 Hiromi Yamakawa, *Modern Theory of Polymer Solutions*, Harper & Row, Publisher Inc., New York, 1971.
- 29 V. Bloomfield and B. H. Zimm, Viscosity, Sedimentation, et Cetera, of Ring- and Straight-Chain Polymers in Dilute Solution, *J. Chem. Phys.*, 1966, **44**, 315–323.
- 30 M. Fukatsu and M. Kurata, Hydrodynamic Properties of Flexible-Ring Macromolecules, *J. Chem. Phys.*, 1966, **44**, 4539–4545.
- 31 E. F. Casassa, Some statistical properties of flexible ring polymers, *J. Polym. Sci. Part A Gen. Pap.*, 1965, **3**, 605–614.
- 32 J. M. Garcia Bernal, M. M. Tirado, J. J. Freire and J. Garcia de la Torre, Monte Carlo calculation of hydrodynamic properties of linear and cyclic polymers in good solvents, *Macromolecules*, 1991, **24**, 593–598.
- 33 Y. Jeong, Y. Jin, T. Chang, F. Uhlik and J. Roovers, Intrinsic Viscosity of Cyclic Polystyrene, *Macromolecules*, 2017, **50**, 7770–7776.
- 34 K. Haydukivska, V. Blavatska and J. Paturej, Universal size

ARTICLE

Journal Name

ratios of Gaussian polymers with complex architecture:
radius of gyration vs hydrodynamic radius, *Sci. Rep.*, 2020,
10, 14127.