


Cite this: *RSC Adv.*, 2023, 13, 14018

# Optimizing the performance of $\text{Au}_y/\text{Ni}_x/\text{TiO}_2\text{NTs}$ photoanodes for photoelectrochemical water splitting†

Shaimaa K. Mohamed,<sup>a</sup> Amany M. A. Bashat,<sup>a</sup> Hassan M. A. Hassan,<sup>a</sup> Nahla Ismail<sup>b</sup> and Waleed M. A. El Rouby<sup>c</sup>

Water splitting using photoelectrochemical (PEC) techniques is thought to be a potential method for creating green hydrogen as a sustainable energy source. How to create extremely effective electrode materials is a pressing concern in this area. In this work, a series of  $\text{Ni}_x/\text{TiO}_2$  anodized nanotubes (NTs) and  $\text{Au}_y/\text{Ni}_x/\text{TiO}_2\text{NTs}$  photoanodes were prepared by electrodeposition *via* cyclic voltammetry and UV-photoreduction, respectively. The photoanodes were characterized by several structural, morphological, and optical techniques and their performance in PEC water-splitting for oxygen evolution reaction (OER) under simulated solar light was investigated. The obtained results revealed the nanotubular structure of  $\text{TiO}_2\text{NTs}$  was preserved after deposition of  $\text{NiO}$  and  $\text{Au}$  nanoparticles while the band gap energy was reduced allowing for effective utilization of solar light with lower charge recombination rate. The PEC performance was monitored and it was found that the photocurrent densities of  $\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  and  $\text{Au}_{30}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  were 1.75-fold and 3.25-fold that of pristine  $\text{TiO}_2\text{NTs}$ , respectively. It was confirmed that the performance of the photoanodes depends on the number of electrodeposition cycles and duration of photoreduction of gold salt solution. The observed enhanced OER activity of  $\text{Au}_{30}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  could be attributed to the synergism between the local surface plasmon resonance (LSPR) effect of nanometric gold which increased solar light harvesting and the p–n heterojunction formed at the  $\text{NiO}/\text{TiO}_2$  interface which led to better charge separation and transportation suggesting its potential application as an efficient and stable photoanode in PEC water splitting for  $\text{H}_2$  production.

Received 27th March 2023

Accepted 2nd May 2023

DOI: 10.1039/d3ra02011h

rsc.li/rsc-advances

## 1. Introduction

Developing renewable, sustainable, and clean energy resources continues to be at the core of scientific research nowadays to address the growing problems of energy demand and environmental pollution.<sup>1–4</sup> One of the most promising green strategies is utilization of solar energy in the production of hydrogen gas by PEC water splitting as it can store the renewable and clean solar energy in chemical bonds while operating at low input bias and room temperature.<sup>1,4,5</sup> In addition, hydrogen is considered an ideal energy carrier due to its renewability, cleanliness, high energy density and zero  $\text{CO}_2$  emissions.<sup>6–9</sup> The efficiency of PEC water splitting is greatly dependent on the following crucial factors: (i) efficient utilization of solar energy

*via* minimizing the band gap of the semiconductor photo-electrode; (ii) the charge transfer rate to the photoelectrode/electrolyte interface and (iii) rapid surface reaction between the photogenerated electrons/holes and the electrolyte.<sup>10</sup> Current research is focusing on enhancing the efficiency of the process through controlling the photoelectrode morphology, tuning the band gap, optimizing electrolyte conditions, and engineering of designed interfaces.<sup>11,12</sup>

One of the most employed photoanodes is  $\text{TiO}_2$  nanotube arrays ( $\text{TiO}_2\text{NTs}$ ) which stands out other titania structures due to stability, highly oriented electron transportation channels and its larger surface area resulting in enhanced diffusion of light, photogenerated carriers and reactants through the entire tubular depth.<sup>13,14</sup> However, large bandgap implying weak solar light absorption and high carrier recombination rates are major drawbacks which can be overcome by chemical modification in the design of the photoanode material.<sup>15</sup> The modification strategies may be directed to band gap reduction *via* chemical doping,<sup>16</sup> retardation of charge recombination by heterojunction formation with other materials<sup>17,18</sup> and enhancing solar energy harvesting through surface sensitization.<sup>19–21</sup>

It is widely acknowledged that doping of transition metal ions can help reducing the band gap thereby extended solar energy

<sup>a</sup>Department of Chemistry, Faculty of Science, Suez University, 43518, Suez, Egypt. E-mail: Shaimaa.Mohamed@Sci.suezuni.edu.eg; h.hassan@suezuniv.edu.eg

<sup>b</sup>Physical Chemistry Department, Centre of Excellence for Advanced Sciences, Renewable Energy Group, National Research Centre, Dokki, 12311, Giza, Egypt

<sup>c</sup>Materials Science and Nanotechnology Department, Faculty of Postgraduate Studies for Advanced Science (PSAS), Beni-Suef University, 62511 Beni-Suef, Egypt. E-mail: waleedmohamedali@psas.bsu.edu.eg

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3ra02011h>



absorption to the visible range while acting as a trap for the photogenerated electrons thus suppressing the carrier recombination rate.<sup>22–24</sup> Ni or Ni – related species (*i.e.* NiO, NiOOH, Ni-NiO) were reported to boost the photocatalytic activity of titania towards H<sub>2</sub> production with a relative uncertainty about the active reaction center (Ni<sup>0</sup> or Ni<sup>2+</sup>).<sup>25–32</sup> Dong *et al.*<sup>30</sup> prepared Ni-doped TiO<sub>2</sub> nanotubes by anodizing Ti-Ni alloys and found that the photoconversion efficiency of PEC water splitting was enhanced 3.35 times the undoped titania which was attributed to improved light absorption and facilitated separation of photo-generated electron-hole pair. Li *et al.*<sup>33</sup> contributed the enhanced photocatalytic and photoelectrochemical activity of NiO/TiO<sub>2</sub> hollow microspheres to the construction of p-n junctions with an inner electric field between TiO<sub>2</sub> and NiO.

Localized surface plasmonic resonance effect of nanometric gold has been reported to enhance PEC water splitting *via* facilitating oxygen evolution reaction.<sup>14,34</sup> Through LSPR the interactions between irradiation photons and Au atoms are enhanced thus increasing visible light absorption on semiconductor surface and reducing diffusion distance of the photogenerated holes to the electrode/electrolyte interface.<sup>34</sup>

Improvement of PEC water-splitting performance can be expected by co-doping transition metal and plasmonic material like Au due to synergistic effects.<sup>34</sup> Oros-Ruiz *et al.*<sup>35</sup> found that Au-NiO/TiO<sub>2</sub>-P25 photocatalyst prepared by deposition-precipitation method were superior to pristine titania in the photocatalytic water splitting reaction for hydrogen production. However, doping of TiO<sub>2</sub>NTs with both NiO and Au and utilization of the prepared nanotubular photoanode in PEC water-splitting for H<sub>2</sub> production is seldom reported. In this work, highly ordered TiO<sub>2</sub>NTs were synthesized by anodization method and a series of Ni<sub>x</sub>/TiO<sub>2</sub>NTs photoanodes were prepared through electrodeposition. Another series of Au<sub>y</sub>/Ni<sub>x</sub>/TiO<sub>2</sub>NTs photoanodes were prepared by facile and simple photoreduction method. The performance of the prepared photoelectrodes was investigated in PEC water-splitting for H<sub>2</sub> production under simulated sun light.

## 2. Materials and methods

### 2.1 Materials

A titanium plate (99.9%) was purchased from AMERICAN ELEMENTS (USA). Ammonium fluoride (95%) and nickel chloride (98%) were purchased from Winlab laboratory chemicals reagents fine chemicals (United Kingdom). Gold(III) chloride trihydrate (HAuCl<sub>4</sub>·3H<sub>2</sub>O), acetone (≥99.8) and ethanol (≥99.5%) were purchased from (Sigma Aldrich, Germany). Tri-sodium citrate (C<sub>6</sub>H<sub>5</sub>O<sub>7</sub>Na<sub>3</sub>·2H<sub>2</sub>O) was purchased from (Qualikems, India). Ethylene glycol (99.9%) was obtained from (Pharmco Product Inc., North America). Sodium sulphate (Oxford Laboratory Reagents, India). All chemicals were utilized without further purification. All the solutions were prepared by deionized water.

### 2.2 Synthesis of the photoelectrodes

**2.2.1 Fabrication of TiO<sub>2</sub>NTs photoanode.** TiO<sub>2</sub>NTs were fabricated through anodization of titanium foil (2 × 1.5 cm).

The titanium foils were ultrasonically cleaned with acetone, ethanol and deionized water for 30 min sequentially and dried in N<sub>2</sub> stream for 3 min. The anodization of the cleaned titanium foil was performed in a mixture of ethylene glycol, 0.3 wt% ammonium fluoride and 2 wt% deionized water at 40 V for 1 h. Then, the anodized Ti foil was ultra-sonicated with ethanol and annealed in air at temperature of 450 °C for 3 h with a heating rate of 5 °C min<sup>-1</sup>.

**2.2.2 Fabrication of Ni<sub>x</sub>/TiO<sub>2</sub>NTs photoanodes.** The prepared TiO<sub>2</sub>NTs was dipped in 50 mL of 0.05 M NiCl<sub>2</sub> electrolyte solution in a conventional electrochemical cell with a three-electrode system, containing a platinum electrode as the counter electrode and an Ag/AgCl electrode as the reference electrode. The cyclic voltammetry method was utilized in the negative potential range of -0.1 to -0.5 V at scanning rate 10 mV s<sup>-1</sup> to obtain the Ni<sub>x</sub>/TiO<sub>2</sub> NTs photoanodes at different number of cycles (where *x* represents the number of cycles = 3, 5, 10, 20 or 30). The prepared photoelectrodes were dried at 80 °C for 2 h and annealed in air at temperature of 450 °C for 3 h with a heating rate of 5 °C min<sup>-1</sup> to obtain the NiO phase.

**2.2.3 Fabrication of (Au<sub>y</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs) photoanodes.** The photoelectrode Ni<sub>20</sub>/TiO<sub>2</sub>NTs was selected to continue the fabrication process based on its performance in the PEC water-splitting reaction. A series of Au<sub>y</sub>/Ni<sub>20</sub>/TiO<sub>2</sub> NTs photoelectrodes were prepared by photoreduction under UV irradiation (where *y* represents irradiation duration = 15, 30, 60 or 120 min). Un-annealed Ni<sub>20</sub>/TiO<sub>2</sub> NTs was immersed in solution of 0.05 mM HAuCl<sub>4</sub> and 1 mM tri-sodium citrate which act as capping and reducing agent and was irradiated with UV light (λ = 365 nm) for different durations. After washing with deionized water, the product was calcined in air at temperature of 450 °C for 2 h with a heating rate of 2 °C min<sup>-1</sup>. The fabrication process scheme is summarized in Fig. 1.

### 2.3 Characterization of the prepared materials

A field emission scanning electron microscope (FE-SEM, ZEISS Sigma 500VP) was used for checking the surface morphologies of the different samples. Elemental analysis was performed by energy-dispersive X-ray spectroscopy (EDS) analysis using equipment fixed on the SEM and operated with an acceleration voltage of 15 kV. High-resolution transmission electron microscope (HRTEM) images were taken by JEOL JEM-2100 electron microscope, where sample was prepared for analysis by scratching from titanium substrate, then ultrasonicated with ethanol. X-ray diffraction (XRD) was performed using a (Bruker D8 Advance, Germany) X-ray powder diffractometer, using Cu Kα radiation (wavelength 1.54 Å, 40 mA, 45 kV). The Shimadzu 2600 spectrophotometer, Japan with Ba<sub>2</sub>SO<sub>4</sub> as the reflectance standard was used for UV-vis analysis. Photoluminescence (PL) spectra were measured using JASCO (FP-8300) spectrofluorometer.

### 2.4 Photoelectrochemical measurements

The photoelectrochemical measurements were performed by Biologic SP-150 potentiostat. The performance of the fabricated photoelectrodes in PEC water-splitting was investigated by its



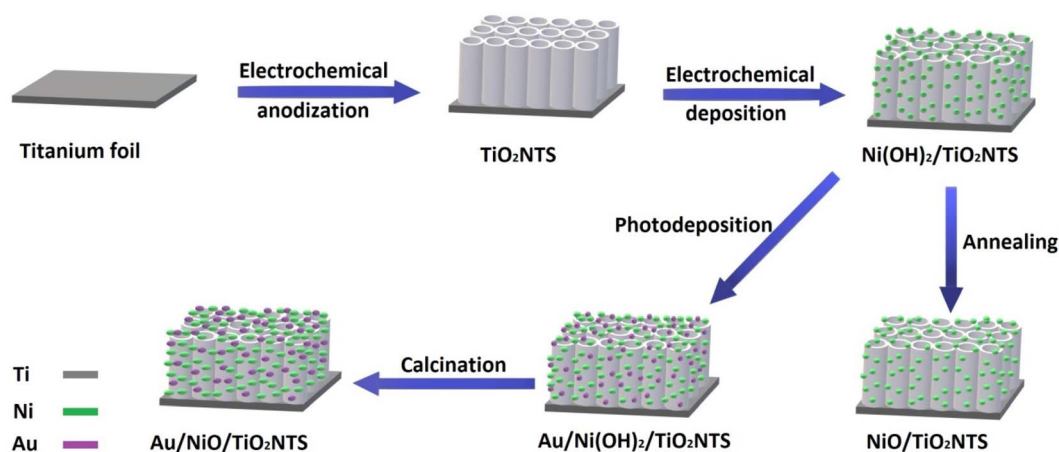


Fig. 1 Scheme of the procedure for the preparation of  $\text{Ni}_x/\text{TiO}_2\text{NTs}$  and  $\text{Au}_y/\text{Ni}_x/\text{TiO}_2\text{NTs}$  photoanodes.

utilization as the working electrode ( $1.5 \text{ cm} \times 1 \text{ cm}$ ) in a three-electrode configuration cell with Pt electrode as a counter electrode and Ag/AgCl reference electrode where  $0.5 \text{ M Na}_2\text{SO}_4$  solution ( $\text{pH} \sim 7$ ) served as the electrolyte. The working photoelectrode was illuminated by xenon lamp-simulated solar light ( $100 \text{ mW}$ ,  $1.5 \text{ AM}$ ). Three techniques were used to monitor the performance namely, linear sweep voltammogram (LSV), chronoamperometric measurements, and electrochemical impedance spectroscopy (EIS). Linear sweep voltammetry was measured in the voltage window starting from  $-0.6 \text{ V}$  to  $+1 \text{ V}$  at a scan rate of  $10 \text{ mV s}^{-1}$  and under chopped applied (ON/OFF) cycles with intervals of  $5 \text{ s}$  in the dark and  $5 \text{ s}$  under illumination. Chronoamperometry was performed under chopped applied ON/OFF cycles with intervals of  $30 \text{ s}$  in the dark and  $30 \text{ s}$  under illumination and the measurements were performed at  $1 \text{ V vs. Ag/AgCl}$  under continuous simulated sunlight illumination for  $6 \text{ minutes}$ . The electrochemical impedance spectroscopy measurements were measured for frequency range  $0.05 \text{ Hz}$  to  $100 \text{ KHz}$  at potential of  $0 \text{ V vs. Ag/AgCl}$  electrode with an amplitude of  $10 \text{ mV}$ . The stability of the fabricated photoelectrodes was measured by chronoamperometry at  $1 \text{ V (vs. Ag/AgCl)}$  for  $1 \text{ h}$  in  $0.5 \text{ M Na}_2\text{SO}_4$  solution.

### 3. Results and discussion

#### 3.1 Structural, chemical, optical and morphological characterization of $\text{Au}_y/\text{Ni}_x/\text{TiO}_2\text{NTs}$ photoelectrodes

The morphologies of the photoelectrodes are investigated by FESEM and are given in (Fig. 2–4). Fig. 2a and b present the top-view and cross-sectional FESEM images of  $\text{TiO}_2\text{NTs}$  photoelectrode, respectively, which demonstrate the nanotube array uniformity with average diameter around  $70 \text{ nm}$ , the wall thickness  $20 \text{ nm}$  and the tubes length ranging from  $1.4\text{--}2.0 \mu\text{m}$ . The length of the prepared  $\text{TiO}_2\text{NTs}$  is favourable for the photoelectrocatalytic water splitting reaction because the maximum penetration depth of light in  $\text{TiO}_2$  nanotubes is  $2.0 \mu\text{m}$ , tubes longer than  $2.0$  is expected to show higher electronic resistance which would retard the photogenerated carriers transportation rate<sup>36,37</sup> and facilitate recombination of the photogenerated electron-hole pairs.<sup>14</sup>

Fig. 3a–e shows the  $\text{Ni}_x/\text{TiO}_2\text{NTs}$  photoelectrodes with NiO nanoparticles deposited onto the top and inner walls of  $\text{TiO}_2\text{NTs}$  while the tubular morphology is preserved. The spacing among nanotubes is no longer obvious, and the nanotube inner diameter and wall become smaller and thicker due to the

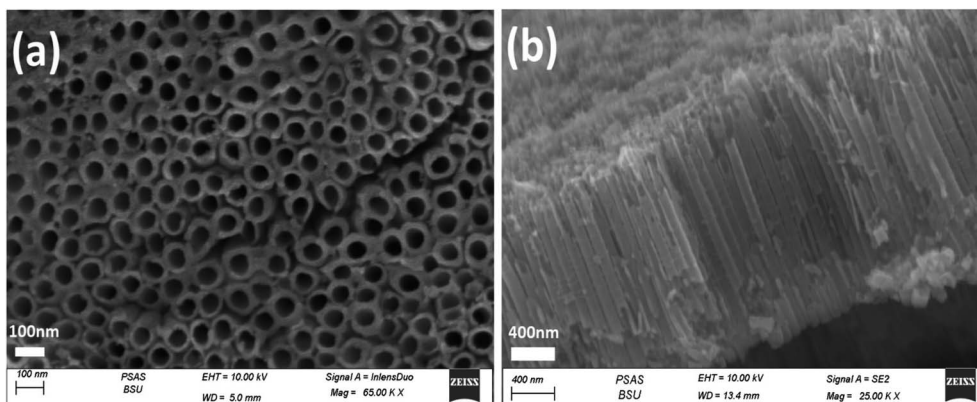


Fig. 2 Top-view (a) and side-view (b) FESEM images of  $\text{TiO}_2\text{NTs}$  photoanode.





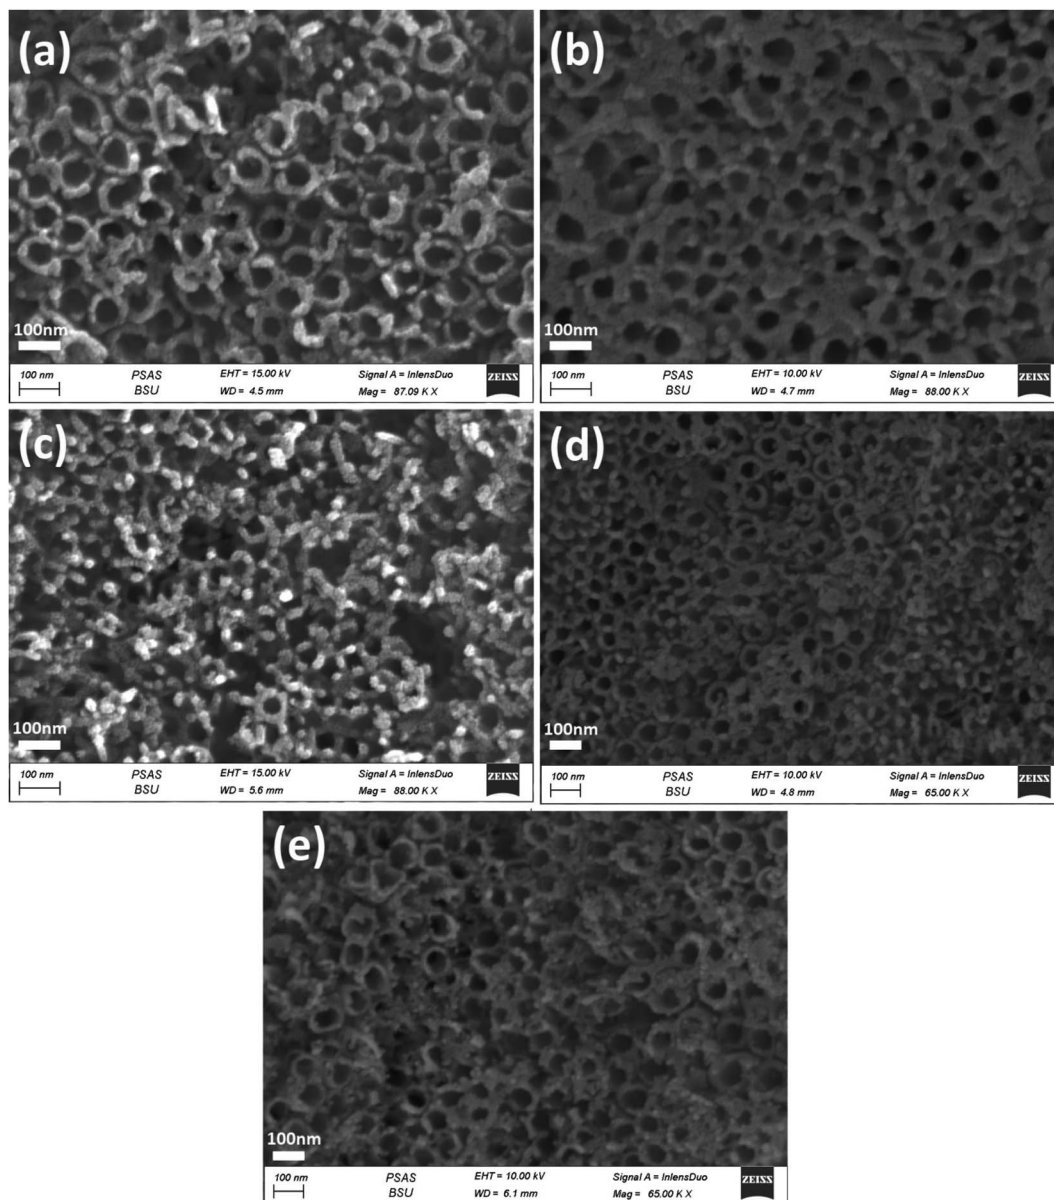


Fig. 3 FESEM images of the top-view of  $\text{Ni}_x/\text{TiO}_2\text{NTs}$  photoanodes synthesised by different electrodeposition cycles (a) 3 cycles, (b) 5 cycles, (c) 10 cycles, (d) 20 cycles and (e) 30 cycles.

deposition of Ni species on the outer and inner surfaces of the tubes. The  $\text{Ni}_x/\text{TiO}_2\text{NTs}$  photoelectrode prepared at 30 cycles showed clogged tubes due to increasing amount of deposited NiO nanoparticles. The morphology of  $\text{Au}_y/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoelectrodes was given by Fig. 4a–d. The images revealed that the photoreduction deposition of gold didn't change the morphology of tubes and a further clogging is observed with increasing the time intervals of reduction.

The energy dispersive X-rays' analysis was performed for all fabricated photoelectrodes (Fig. S1–S10†), and the calculated element's atomic percent were presented in Table 1. The presence of the elements Ti, Ni and Au is confirmed in a manner corresponding to the preparation method. The amount of Ni was raised gradually by increasing the number of cycles of

electrodeposition from 5 to 20 cycle. It was found in photoelectrodes containing gold that the amount of Au increased as the time intervals of photoreduction deposition increased. The EDS elemental mapping results is present in Fig. 5 for one selected photoelectrode ( $\text{Au}_{30}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$ ) where nickel (Ni), gold (Au) elements were uniformly and homogeneously deposited on the surface of titania tubes. This would lead to well-dispersed active sites along the tubes which enhance the efficiency of the photoelectrocatalytic reaction.<sup>38</sup>

HRTEM images for one selected photoelectrode  $\text{Au}_{30}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  showed in Fig. 6 confirmed the nano-tubular structure. The surface of  $\text{TiO}_2\text{NTs}$  was rough where gold (Au) and nickel (NiO) particles can be found dispersed all over the surface of nanotubes. The lattice fringes of 0.31 nm corresponds to the



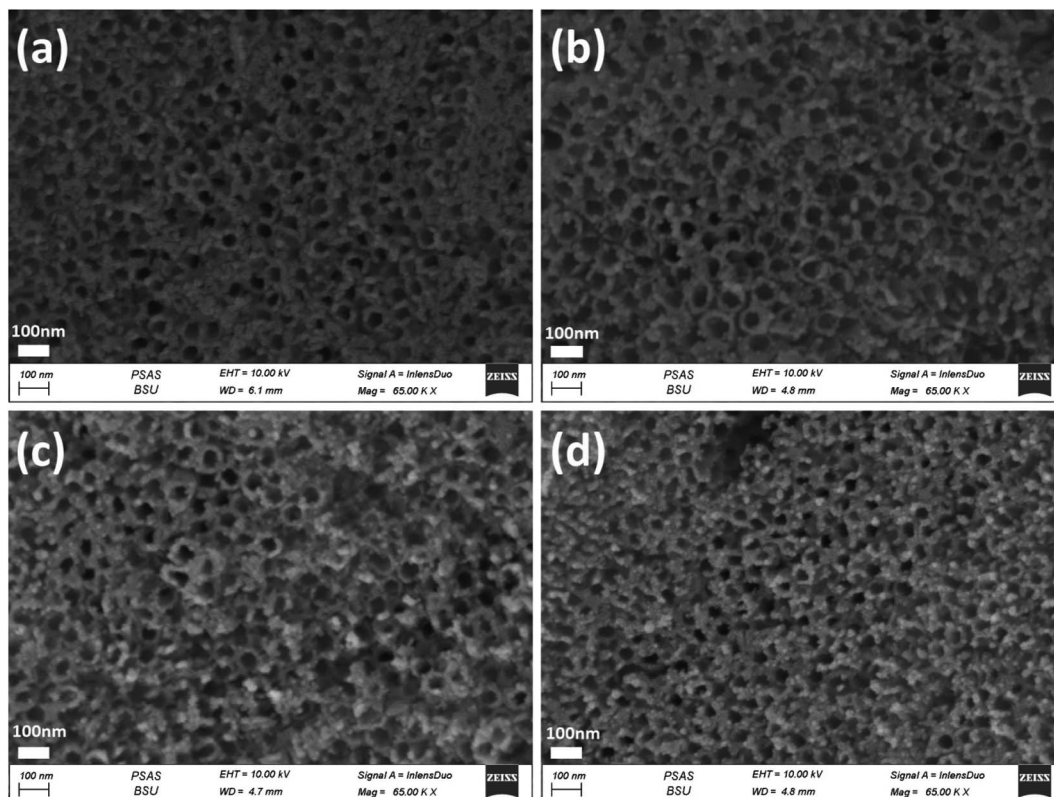


Fig. 4 FESEM images of the top-view of  $\text{Au}_x/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoanodes synthesised by different time intervals of photodeposition (a) 15 min, (b) 30 min, (c) 60 min and (d) 120 min.

Table 1 Elemental composition and band gap values of the prepared photoanodes

Photoelectrode	Ti	O	Ni	Au	Band gap (eV)
$\text{TiO}_2$	14.70	85.30			3.05
$\text{Ni}_3/\text{TiO}_2\text{NTs}$	26.19	73.47	0.34		2.85
$\text{Ni}_5/\text{TiO}_2\text{NTs}$	26.15	73.47	0.38		2.83
$\text{Ni}_{10}/\text{TiO}_2\text{NTs}$	26.98	72.60	0.42		2.82
$\text{Ni}_{20}/\text{TiO}_2\text{NTs}$	29.84	69.70	0.46		2.80
$\text{Ni}_{30}/\text{TiO}_2\text{NTs}$	12.69	86.86	0.45		2.81
$\text{Au}_{15}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$	12.62	86.82	0.36	0.20	2.93
$\text{Au}_{30}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$	14.39	84.96	0.42	0.23	2.89
$\text{Au}_{60}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$	13.59	85.70	0.39	0.33	2.95
$\text{Au}_{120}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$	13.10	86.03	0.51	0.37	2.96

reflection from the (101) plane of anatase  $\text{TiO}_2$  is identified as seen in Fig. 6b.<sup>37</sup> Fig. 6 c represented the selected area electron diffraction (SAED) which confirmed the crystalline structure of the photoelectrode and the presence of diffraction rings corresponding to (101), (103), (200), and (220) planes of  $\text{TiO}_2$ .<sup>39</sup> The (220) and (311) planes corresponded to metallic gold<sup>40</sup> where the plane (110) may be indexed to NiO phase.<sup>41</sup>

The XRD diffractograms of the prepared photoelectrodes were given in Fig. 7. All prepared samples showed the presence of three phases which are metallic titanium, anatase and rutile. The peaks corresponding to anatase appeared at  $2\theta = 25.1^\circ$ ,

$37.7^\circ$  and  $48^\circ$  characteristic of (101), (004) and (200) planes, respectively (JCPDS 21-1272).<sup>19,42</sup> The peaks at  $2\theta = 38.2^\circ$ ,  $40^\circ$ ,  $52.8^\circ$ ,  $70.4^\circ$  and  $76.1^\circ$  corresponded to (002), (101), (102), (103) and (112) planes, respectively of metallic titanium, (JCPDS 44-1294), attributed to the metallic substrate.<sup>43</sup> Small peaks due to rutile as a minor phase was located at  $2\theta = 27.2^\circ$ ,  $35^\circ$ ,  $53.85^\circ$ ,  $55^\circ$  and  $68.8^\circ$  characteristic of (110), (101), (200), (211), and (220) planes (JCDPDP 01-089-8304).<sup>44</sup> The anatase: rutile ratio was 2 : 1 in  $\text{TiO}_2\text{NTs}$  sample suggesting enhanced performance in PEC due to improved hole transfer rate across  $\text{TiO}_2\text{NTs}/$  electrolyte interface.<sup>42,45</sup> The crystalline size of the anatase phase was found to be 25 nm confirming the nanostructure of the prepared tubes. There were no peaks detected for gold or nickel phases may be due to its low concentration<sup>42,46</sup> and high dispersion. Another possible explanation may be provided by considering the limitations of X-ray powder diffraction technique.<sup>47</sup> Amorphous phases do not give rise to diffraction peaks. Phase overlap may hinder phase identification while due to matrix effects, strongly diffracting phases would obscure weakly diffracting one. Thus, any of the above-mentioned reasons may account for the absence of diffraction peaks for gold and nickel – containing phases.

Fig. 8 represents XPS spectra for  $\text{Au}_{30}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoelectrode which was analysed to determine surface chemical composition and oxidation states. Peaks at 459.4 and 465.1 eV of the titanium spectra corresponded to photoelectronic splitting of  $2p_{1/2}$  and  $2p_{3/2}$   $\text{Ti}^{4+}$  orbitals.<sup>48</sup> The XPS spectra for Au 4f





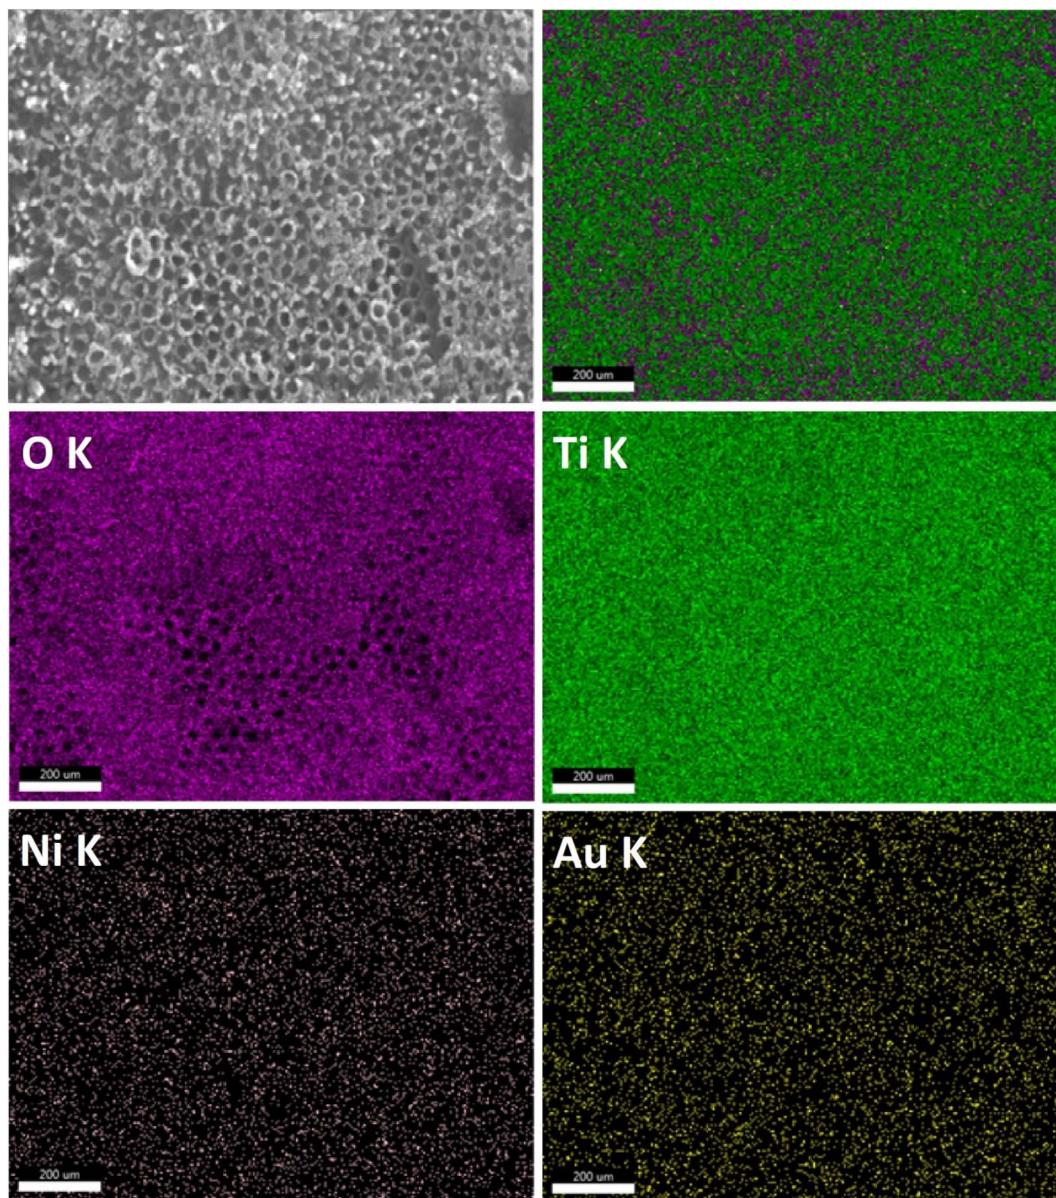


Fig. 5 The EDS elemental mapping of  $\text{Au}_{30}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$ .

showed two peaks at binding energies of 84.0 and 87.6 eV due to  $\text{Au } 4f_{7/2}$  and  $\text{Au } 4f_{5/2}$ , respectively which confirmed the presence of  $\text{Au}^0$ .<sup>49</sup> The deconvoluted spectra of  $\text{O } 1s$  showed two peaks at

530.6 eV was attributed to the lattice oxygen of  $\text{TiO}_2$  or the metal–oxygen bond<sup>50</sup> and 532.1 eV resulted from the existence of  $\text{O–H}$  bond.<sup>51</sup> The  $\text{Ni } 3p$  region was used to analyse the

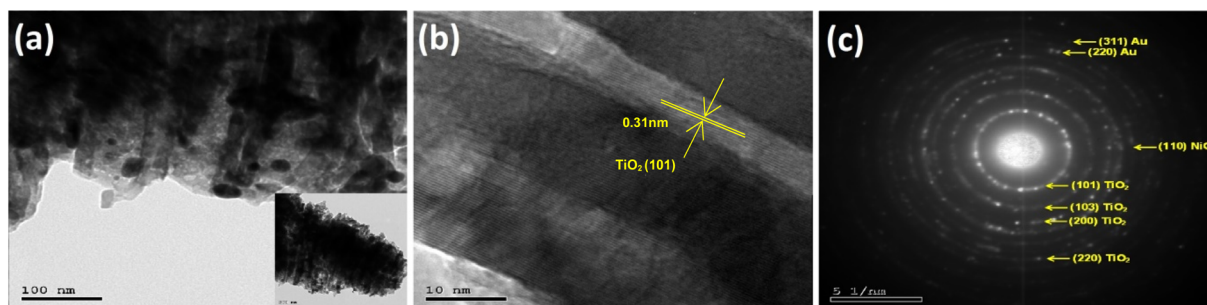


Fig. 6 (a and b) HRTEM images of  $\text{Au}_{30}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  and (c) SAED patterns of photoanode.

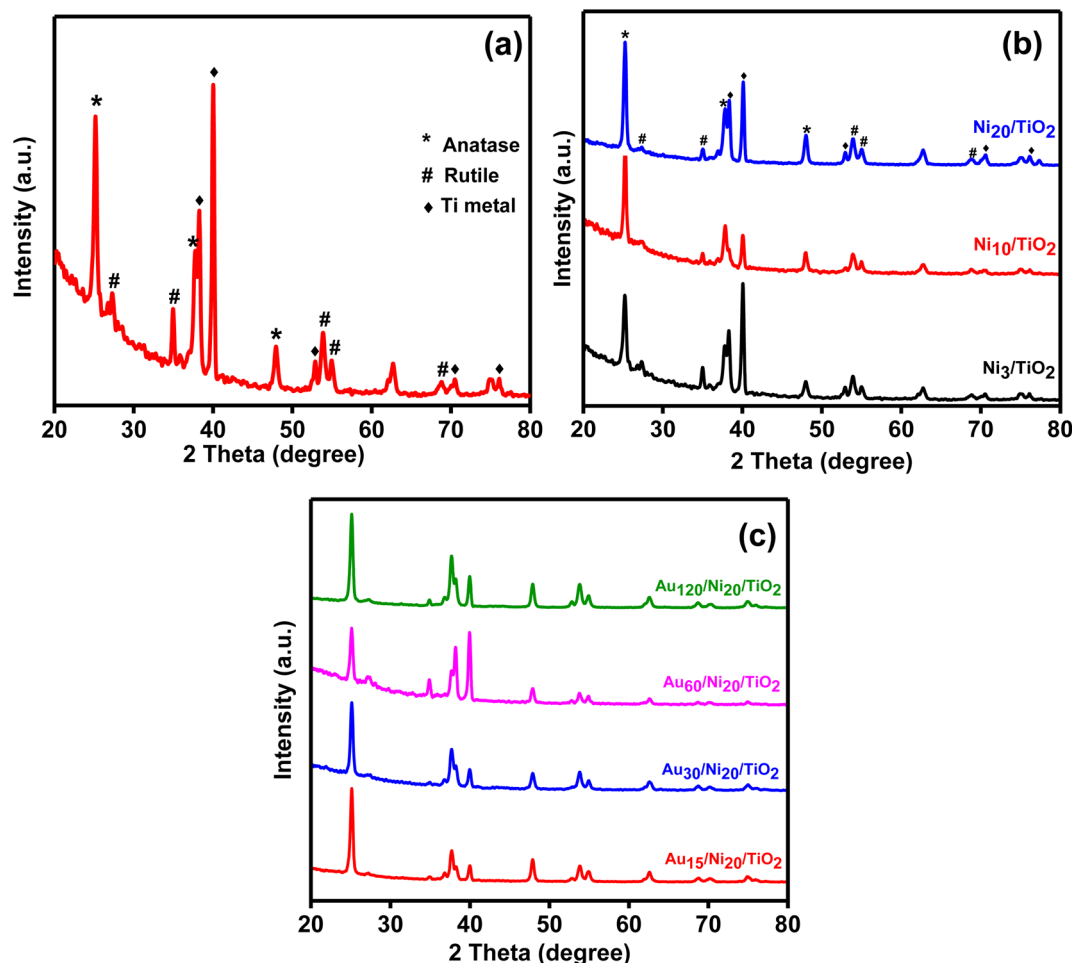


Fig. 7 XRD diffractograms for the prepared TiO<sub>2</sub>NTs photoanode (a), Ni<sub>x</sub>/TiO<sub>2</sub>NTs photoanodes (b) and Au<sub>y</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs photoanodes (c).

oxidation state of nickel in the prepared photoelectrode similar to Amaya-Dueñas *et al.*<sup>52</sup> and peak at 63.7 eV was observed and it was assigned to NiO.<sup>53</sup>

Fig. 9 depict the UV-vis diffuse reflectance absorption spectra (DRS) of the pure TiO<sub>2</sub>NTs, Ni<sub>x</sub>/TiO<sub>2</sub> and Au<sub>y</sub>/Ni<sub>x</sub>/TiO<sub>2</sub>NTs photoelectrodes in the range of 200–600 nm. The strong absorption observed in a wavelength region below 403 nm for the pure TiO<sub>2</sub>NTs is due to the intrinsic inter-band transition absorption of TiO<sub>2</sub>NTs.<sup>54,55</sup> The light absorption edge was red shifted to the visible light for Ni<sub>x</sub>/TiO<sub>2</sub>NTs (Fig. 9a) photoelectrodes which can be explained by formation of a p–n heterojunction was formed across TiO<sub>2</sub>/NiO interface leading to electron excitation by visible light photons. Au<sub>y</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs (Fig. 9b) photoelectrodes showed enhanced absorption in the visible light region than pristine TiO<sub>2</sub>NTs while absorption peak in the range of 500–600 nm appeared in the spectrum. This peak resulted from the LSPR effect induced by gold nanoparticle.<sup>34,56,57</sup> It has been reported that the LSPR effect leads to enhanced OER performance of photoanodes.<sup>34,58</sup> To estimate the band gap energy of the prepared photoelectrodes, Kubelka–Munk transformation on the obtained UV-vis absorption data was used to produce Tauc plot which was represented by Fig. 9c and d. A Tauc plot was constructed by plotting  $(\alpha h\nu)^{1/2}$  versus  $h\nu$

and the band gap energy ( $E_g$ ) values were obtained by extrapolating linear region of the curves to meet x-axis<sup>59</sup> and cited in Table 1. The  $E_g$  value of TiO<sub>2</sub>NTs was found to be 3.05 eV in accordance with the reported data of titania nanotubes.<sup>60</sup> TiO<sub>2</sub>NTs band gap is due to Ti 3d and O 2p hybridized states where the conduction band's lowest edge being formed by Ti d<sub>xy</sub> states and the O 2p<sub>x</sub>p<sub>y</sub> states forms the highest edge of valence band.<sup>14</sup> Ni<sub>x</sub>/TiO<sub>2</sub>NTs and Au<sub>y</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs showed a narrowed band gap suggesting photoinduction of e<sup>−</sup>/h<sup>+</sup> pair by visible light thus maximizing utilization of solar light. The obtained results are in accordance with Oros-Ruiz *et al.* who reported reduction of band gap value of TiO<sub>2</sub>–P25 from 3.1 to 2.9 eV after loading of Au–NiO.<sup>35</sup>

Photoluminescence (PL) spectra of the prepared photoelectrodes were investigated to study surface processes including photoexcited e<sup>−</sup>/h<sup>+</sup> recombination rate and the efficiency of charge trapping and given in Fig. 10. The PL spectra of TiO<sub>2</sub>NTs showed the highest intensity and exhibited peaks at 420 and 452 nm assigned to self-trapped excitons<sup>61</sup> where peaks at 469, 482 and 502 nm can be ascribed to oxygen vacancies and surface defects.<sup>62</sup> The PL spectra of Ni<sub>x</sub>/TiO<sub>2</sub>NTs photoelectrodes showed the same peaks but with reduced intensity indicating lower rate of photoexcited e<sup>−</sup>/h<sup>+</sup> recombination and



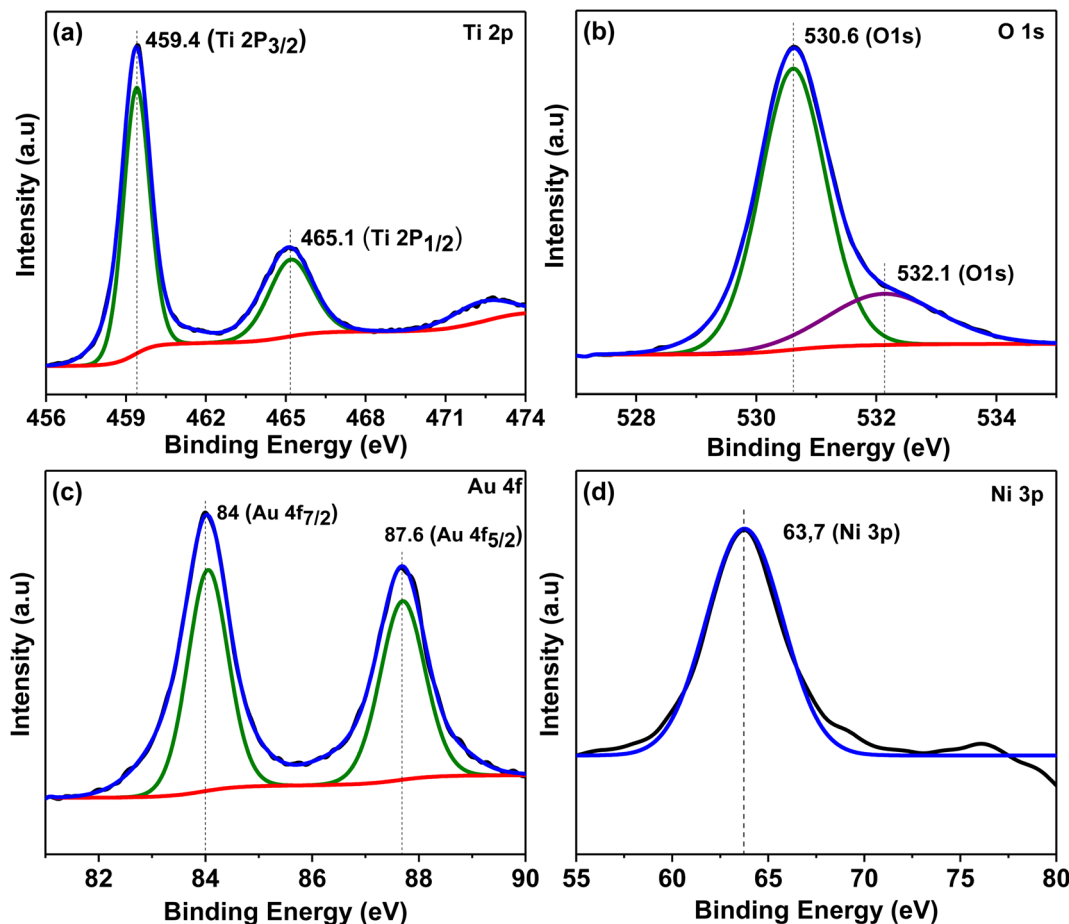


Fig. 8 XPS spectra for  $\text{Au}_{30}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoelectrode (a) Ti 2p, (b) O 1s, (c) Au 4f and (d) Ni 3p.

improved efficiency of charge separation which is beneficial in the PEC process.<sup>43</sup> Further reduction in the intensity was observed in  $\text{Au}_y/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoelectrodes due to emerging trapping sites resulted from Au doping. The intensities of PL peaks of  $\text{Ni}_x/\text{TiO}_2\text{NTs}$  and  $\text{Au}_y/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  samples were generally lower than pristine titania nanotubes. The PL intensities of  $\text{Au}_y/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  were decreased in the order  $\text{Au}_{120} \approx \text{Au}_{60} > \text{Au}_{30} \approx \text{Au}_{15}$ . It is known that PL signals of semiconductor materials result from the recombination of photo-induced charge carriers thus in general, the lower the PL intensity, the lower the recombination rate of photoinduced electron-hole pairs, and hence higher photocatalytic activity.<sup>63</sup> However, the PL mechanisms of semiconductor nanoparticles are very complex, and it is not possible to extrapolate the contribution of the single factors since various parameters, as for instance particle size, recombination velocity, and presence of defects, are responsible in a different way for the shape and intensity of PL spectra. In this work, different periods were used for photo deposition of Au which might affected the particle size of Au giving rise to larger size at extended deposition duration. This could affect the rate of carriers' recombination and hence the PL intensity. Same behavior was reported by Khore *et al.*<sup>49</sup> where the PL intensities of  $\text{Au}@\text{TiO}_2$  composites were decreased by increasing Au loading to 2% then increased when

the loading reached 3% Au. Also, Lin *et al.*<sup>64</sup> reported the intensity of the PL emission signals decreased with the decreasing of the Au NPs sizes indicating the radiation recombination of the photo-induced carriers were suppressed when the Au NPs became smaller.

### 3.2 Photoelectrochemical performance of the prepared photoelectrodes

Linear sweep voltammetry measurement (Fig. 11) illustrated that  $\text{TiO}_2\text{NTs}$ ,  $\text{Ni}_x/\text{TiO}_2\text{NTs}$  and  $\text{Au}_y/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoelectrodes are all n-type semiconductors and exhibited an OER activity since under light irradiation, the photocurrent increases when the applied anodic potential is increased.<sup>65</sup>  $\text{TiO}_2\text{NTs}$  showed the lowest photocurrent density of  $0.08 \text{ mA cm}^{-2}$  attributed to the wide band gap (3.05 eV) and higher rate of recombination of photogenerated charge carriers.<sup>27</sup>  $\text{Ni}_x/\text{TiO}_2\text{NTs}$  photoanodes (Fig. 11a) exhibited higher water photo-oxidation activities and higher photocurrent densities than  $\text{TiO}_2\text{NTs}$ . This behavior is attributed to efficient separation of photogenerated charge carriers due to the Ni 3d states serving as trapping sites for photogenerated electrons from the VB which is in accordance with the PL results. The same enhancement in behavior was also reported for Ni doped titania photoanodes in PEC water splitting by many groups.<sup>26–28,30,66</sup> The



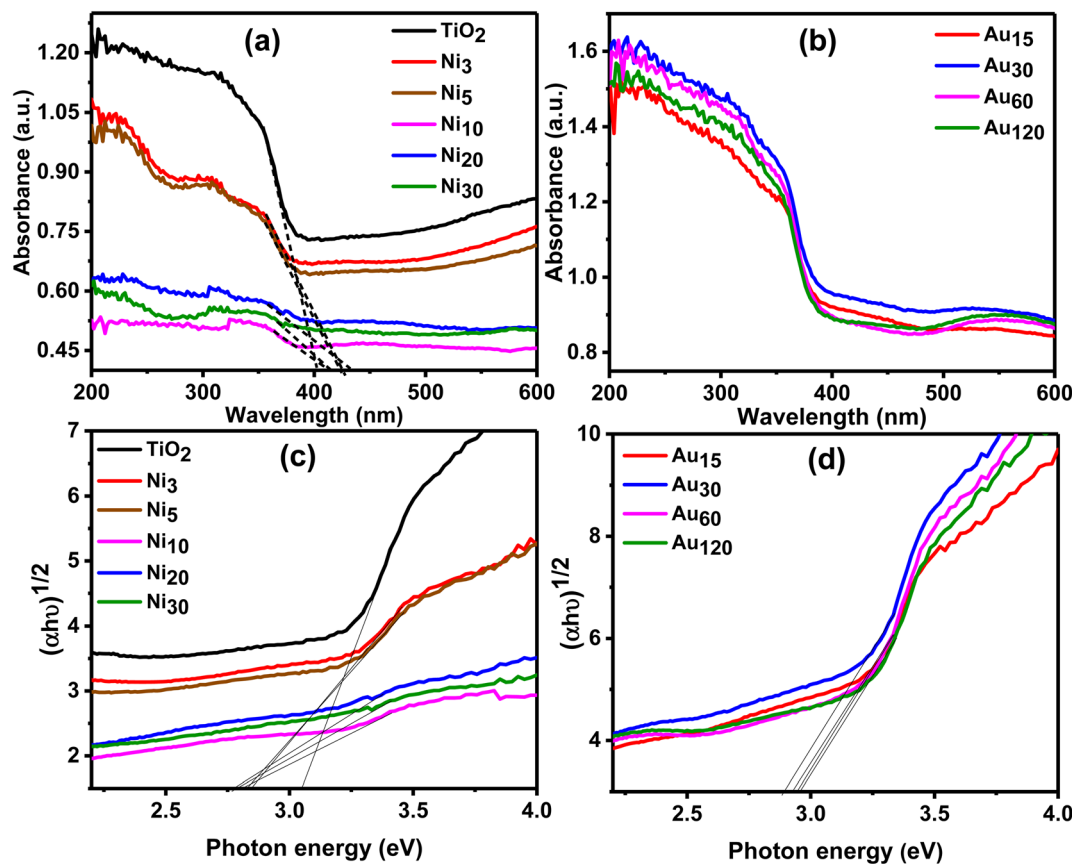


Fig. 9 Diffuse reflectance UV-visible spectra of (a)  $\text{TiO}_2\text{NTs}$  and  $\text{Ni}_x/\text{TiO}_2\text{NTs}$  photoanodes, and (b)  $\text{Au}_y/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoanodes. Tauc plot of (c)  $\text{Ni}_x/\text{TiO}_2\text{NTs}$  and (d)  $\text{Au}_y/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$ .

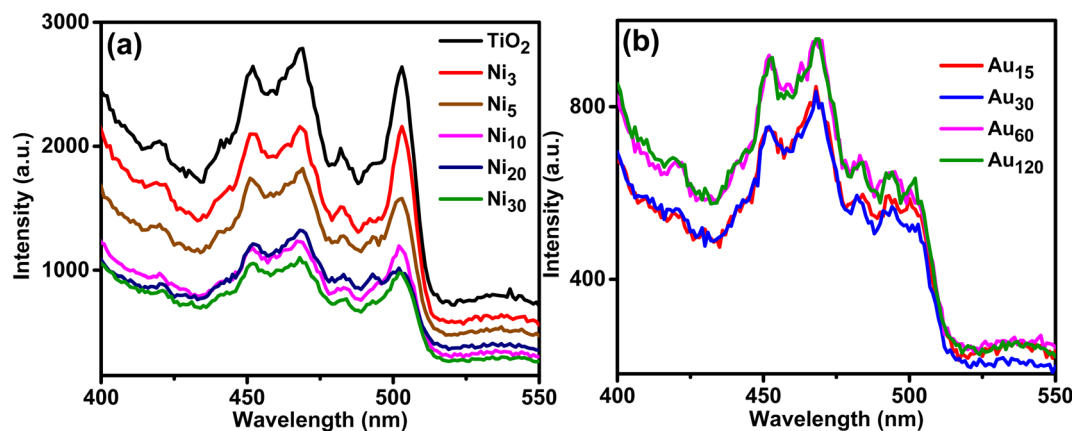


Fig. 10 PL spectra of (a)  $\text{TiO}_2\text{NTs}$  and  $\text{Ni}_x/\text{TiO}_2\text{NTs}$  photoanodes, and (b)  $\text{Au}_y/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoanodes.

increase in the photocurrent density was dependent on the number of electrodeposition cycles during preparation and was found in the order  $\text{Ni}_3/\text{TiO}_2\text{NTs} < \text{Ni}_5/\text{TiO}_2\text{NTs} < \text{Ni}_{10}/\text{TiO}_2\text{NTs} < \text{Ni}_{20}/\text{TiO}_2\text{NTs} \approx \text{Ni}_{30}/\text{TiO}_2\text{NTs}$ . The photocurrent density of  $\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  was  $0.14 \text{ mA cm}^{-2}$  that is 1.75-fold of pristine  $\text{TiO}_2\text{NTs}$ , and it can be concluded that 20 cycles of electrodeposition was efficient in producing significant enhancement in the photoanode performance. Photodeposition of gold

nanoparticles boosted the OER activity of  $\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoanode as can be seen in Fig. 11b which revealed the photocurrent density of  $\text{Au}_y/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoanodes was higher than both pristine  $\text{TiO}_2\text{NTs}$  and  $\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  due to synergistic effect of co-doping of Ni and Au. The photocurrent densities were found in the order  $\text{Au}_{120}/\text{Ni}_{20}/\text{TiO}_2\text{NTs} < \text{Au}_{60}/\text{Ni}_{20}/\text{TiO}_2\text{NTs} < \text{Au}_{15}/\text{Ni}_{20}/\text{TiO}_2\text{NTs} < \text{Au}_{30}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$ . The photocurrent density of  $\text{Au}_{30}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  was  $0.26 \text{ mA cm}^{-2}$  that is



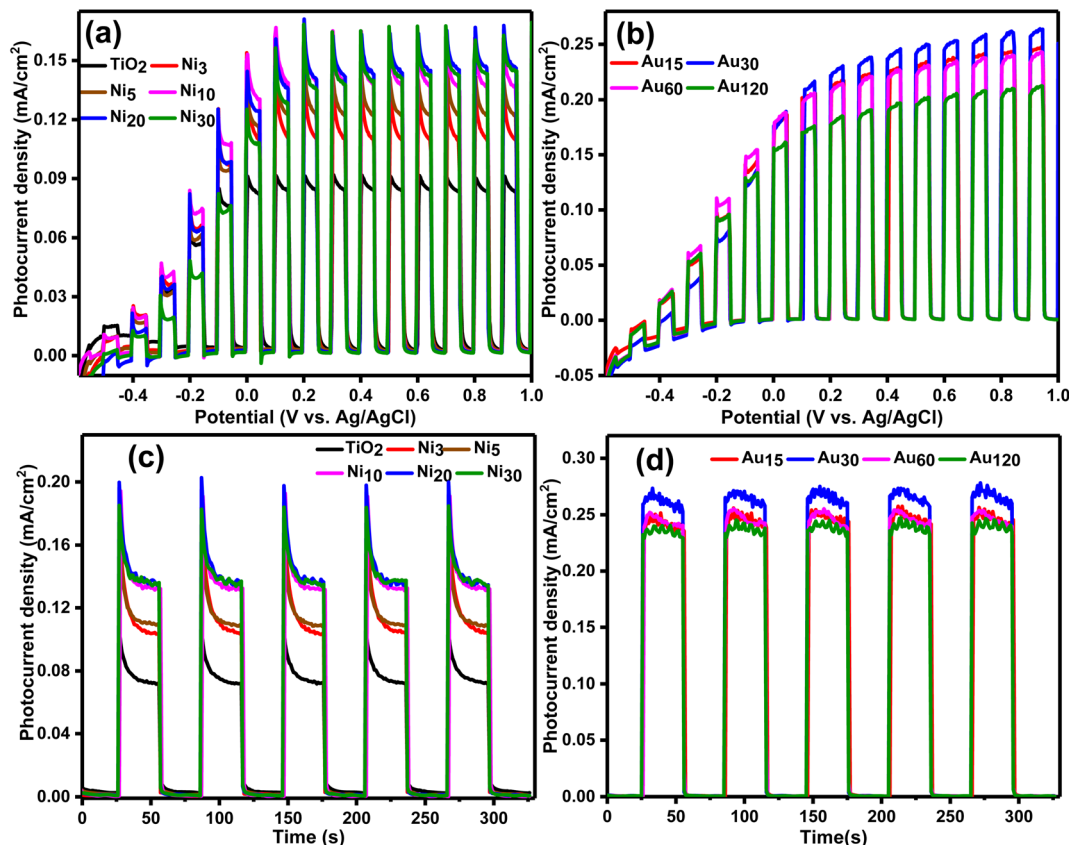


Fig. 11 (LSV) curves at a scan rate of 10 mV for (a) TiO<sub>2</sub>NTs and Ni<sub>x</sub>/TiO<sub>2</sub>NTs photoanodes, and (b) Au<sub>y</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs photoanodes. The chopped light chronoamperometric measurements at a scan rate of 10 mV for (c) TiO<sub>2</sub>NTs and Ni<sub>x</sub>/TiO<sub>2</sub>NTs photoanodes, and (d) Au<sub>y</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs photoanodes.

3.25-fold of pristine TiO<sub>2</sub>NTs, this enhancement of performance can be explained in light of (PL) results where Au<sub>30</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs was the most efficient photoanode in charge separation thus suppressing recombination of photogenerated charge carrier which led to enhanced photoelectrochemical performance.

Chronoamperometric measurements measured at 1 V vs. Ag/AgCl on the prepared photoanodes under chopped light irradiation was presented in Fig. 11. All the prepared photoanodes showed excellent solar light response as illustrated by the fast photo-response in the ON/OFF cycles and the good reproducibility. The measured photocurrent density of TiO<sub>2</sub>NTs was 0.07 mA cm<sup>-2</sup> which is comparable with published data on TiO<sub>2</sub> photoanodes.<sup>67</sup> Photoanodic current spikes can be observed for TiO<sub>2</sub>NTs and Ni<sub>x</sub>/TiO<sub>2</sub>NTs photoanodes (Fig. 11c) at the onset of the potential attributed to the undesired fast recombination of photo-generated carriers at photoanode surface which limit their transport to the electrolyte. In this situation charge recombination is kinetically faster than charge transport (electrons to bulk regions or holes to the electrolyte).<sup>65</sup> The measured photocurrent density of the prepared Ni<sub>x</sub>/TiO<sub>2</sub>NTs photoanodes was comparable with the data from LSV showing the same dependence on the number of electrodeposition cycles. Upon photoelectrodeposition of gold on Ni<sub>20</sub>/TiO<sub>2</sub>NTs, the photoanodic current spikes disappeared confirming efficient charge

separation. The highest photocurrent density of Au<sub>y</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs photoanodes was exhibited by Au<sub>30</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs (0.26 mA cm<sup>-2</sup>) consistent with LSV measurements. The measured values of photocurrent density were dependant on the number of gold photo-electrodeposition cycle reaching a maximum at 30 cycles. Increase the number of cycles above that limit would cause a slight reduction in the photocurrent density probably due to creation of additional recombination sites.<sup>67</sup> The observed enhanced OER activity of Au<sub>30</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs could be attributed to LSPR effect of nanometric gold which increased solar light harvesting and the synergism between Ni and Au which led to better charge separation and transportation. The obtained data of chronoamperometry was in accordance with the data obtained from optical measurements and linear sweep voltammetry.

Electrochemical impedance spectroscopy was conducted to elucidate the charge transfer characteristics at the photoelectrode/electrolyte interface and the Nyquist plots are given in Fig. 12. It is well known that the radius of semicircle denotes the electron transfer at interface,<sup>68</sup> where a larger radius generally indicates larger electron transfer resistance and lower charge separation efficiency.<sup>58,69,70</sup> As shown in Fig. 12a, the semicircle radius of all Ni<sub>x</sub>/TiO<sub>2</sub>NTs photoanodes was smaller than that of TiO<sub>2</sub>NTs indicating lower charge transfer resistance, long charges lifetime and higher charge separation

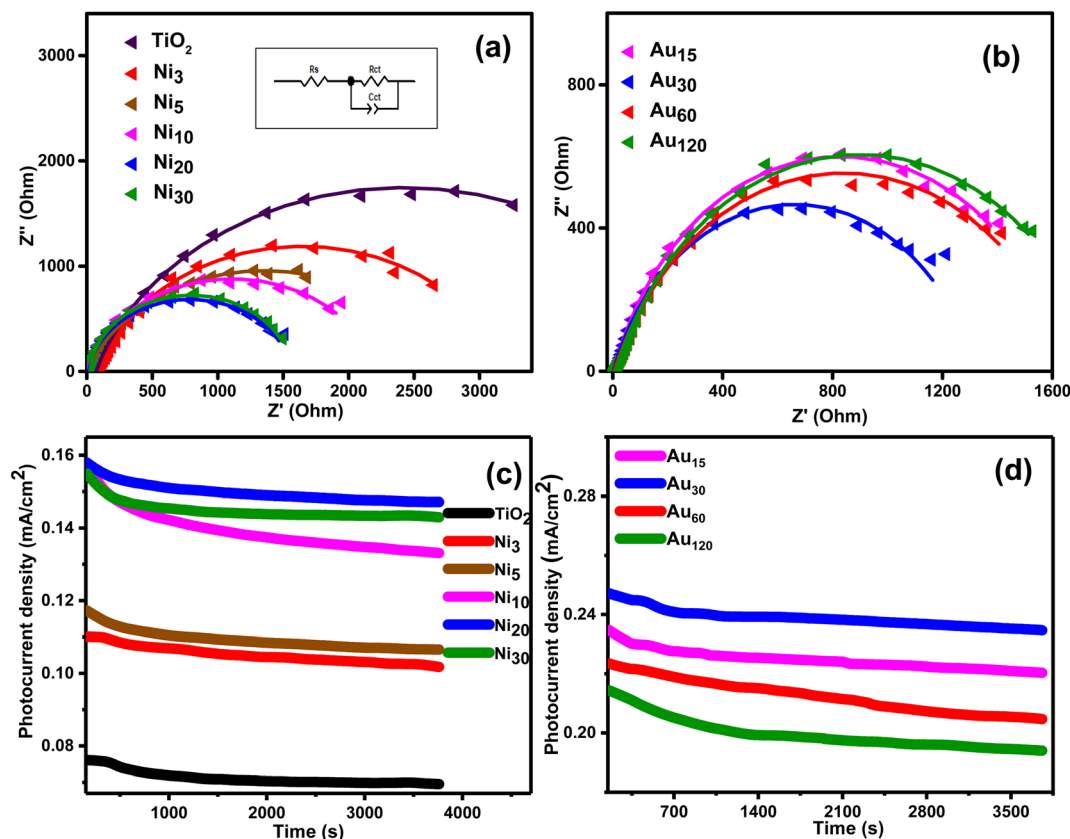


Fig. 12 Electrochemical impedance spectroscopy plot of (a)  $\text{TiO}_2\text{NTs}$  and  $\text{Ni}_x/\text{TiO}_2\text{NTs}$  photoanodes, and (b)  $\text{Au}_y/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoanodes. The proposed equivalent circuit (inset (a)). The stability measurement at 1.0 V for 1 h of (c)  $\text{TiO}_2\text{NTs}$  and  $\text{Ni}_x/\text{TiO}_2\text{NTs}$  photoanodes, and (d)  $\text{Au}_y/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoanodes.

efficiency.<sup>71</sup> Further reduction in the semicircle radius was observed in  $\text{Au}_y/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoanodes (Fig. 12b) and  $\text{Au}_{30}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  showed the smallest charge transport resistance. The equivalent circuit diagram was suggested (inset Fig. 13a) and the values of the charge transfer resistance  $R_{ct}$  were calculated. The  $R_{ct}$  of pristine  $\text{TiO}_2\text{NTs}$  was 4.80 k $\Omega$  which was reduced in  $\text{Ni}_x/\text{TiO}_2\text{NTs}$  photoanodes following the order  $\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  (1.54 k $\Omega$ ) <  $\text{Ni}_{30}/\text{TiO}_2\text{NTs}$  (1.58 k $\Omega$ ) <  $\text{Ni}_{10}/\text{TiO}_2\text{NTs}$  (2.19 k $\Omega$ ) <  $\text{Ni}_5/\text{TiO}_2\text{NTs}$  (2.54 k $\Omega$ ) <  $\text{Ni}_3/\text{TiO}_2\text{NTs}$  (3.14 k $\Omega$ ). The values of  $R_{ct}$  of  $\text{Au}_y/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoanodes were  $\text{Au}_{30}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  (1.34 k $\Omega$ ) <  $\text{Au}_{15}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  (1.65 k $\Omega$ ) <  $\text{Au}_{60}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  (1.67 k $\Omega$ ) <  $\text{Au}_{120}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  (1.75 k $\Omega$ ). The reduction in  $R_{ct}$  values means more holes are participating in water oxidation reaction and better separation efficiency. The photoanode  $\text{Au}_{30}/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  exhibited the smallest charge transfer resistance and higher charge separation efficiency in accordance with other electrochemical and optical measurement suggesting its application as efficient photoanode in PEC water splitting for  $\text{H}_2$  production.

The stability of the different photoanodes was determined by chronoamperometry at 1 V vs. Ag/AgCl under constant light irradiation and the results obtained during the first hour are shown in Fig. 12. The photocurrent density was marginally reduced for all photoanodes suggesting good stability. Comparison with other reported photoanodes (Table 2) suggested reasonably high photocurrent density of the prepared photoanode which confirmed its potential application as efficient and stable photoanode in PEC water splitting for  $\text{H}_2$  production.

The following mechanisms were proposed based on the obtained results from optical and electrochemical measurements after considering the published mechanisms in literature.<sup>1,4,10,14,56,72–74</sup> First for  $\text{Ni}_x/\text{TiO}_2\text{NTs}$  photoanodes; a p-n heterojunction was formed across the  $\text{TiO}_2\text{NTs}$  (n-type semiconductor)/NiO (p-type semiconductor) interface. Upon visible light excitation charge carriers were photogenerated in

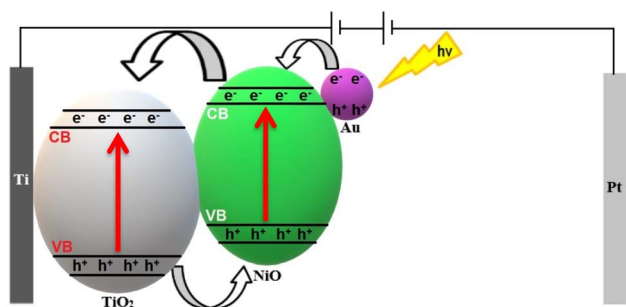


Fig. 13 The proposed mechanism for charge transfer in  $\text{Au}_y/\text{Ni}_{20}/\text{TiO}_2\text{NTs}$  photoanodes during PEC.





Table 2 Photocurrent density comparison with other reported photoanodes

Photoanode	Electrolyte	Voltage	Photocurrent density (mA cm <sup>-2</sup> )	Ref.
Ag-N, S-C/TiO <sub>2</sub> @CC	0.5 M phosphate buffer solution	1.23 V vs. RHE	0.089	75
m-RGO/TiO <sub>2-x</sub>	0.1 M Na <sub>2</sub> SO <sub>4</sub>	0.2 V vs. SCE	0.018	76
CdSe/TiO <sub>2</sub> NTs	0.2 M Na <sub>2</sub> S	0.5 V vs. SCE	0.167	77
AgVO <sub>3</sub> /V <sub>2</sub> O <sub>5</sub> -TiO <sub>2</sub>	0.2 M Na <sub>2</sub> SO <sub>3</sub> and 0.1 M Na <sub>2</sub> S		0.115	78
GQDs/TiO <sub>2</sub> -20	0.5 M Na <sub>2</sub> SO <sub>4</sub>	0.5 V vs. SCE	0.072	79
Cr-S-codoped TiO <sub>2</sub>	1.0 M KOH	0.40 V vs. Ag/AgCl	0.202	80
TNT-15Ti <sub>3</sub> C <sub>2</sub> T <sub>x</sub>	0.5 M Na <sub>2</sub> SO <sub>4</sub>	0.6 V vs. Ag/AgCl	0.177	81
5 nm Au NPs@TNAs	1 M KOH	1.23 V vs. RHE	0.140	37
Au(556)/TiO <sub>2</sub> NTPC	—	1.23 V vs. RHE	0.150	82
W-h-TiO <sub>2</sub>	0.1 M Na <sub>2</sub> SO <sub>4</sub>	0.6 V vs. Ag/AgCl	0.080	16
Ni ALD/black TiO <sub>2</sub>	1 M KOH	0.23 V vs. Ag/AgCl	0.165	26
Ni-TiO <sub>2</sub> nanorods	0.1 M Na <sub>2</sub> SO <sub>4</sub>	0 V vs. (Ag/AgCl)	0.140	66
CFTS/Ni-TiO <sub>2</sub>	0.1 M Na <sub>2</sub> SO <sub>4</sub>	0 V vs. (Ag/AgCl)	0.190	66
Au <sub>30</sub> /Ni <sub>20</sub> /TiO <sub>2</sub> NTs	0.5 M Na <sub>2</sub> SO <sub>4</sub>	1 V vs. Ag/AgCl	0.260	Current work

both semiconductors followed by migration of electrons from the CB of NiO to the CB of TiO<sub>2</sub> then through the electric circle to the Pt wire. Meanwhile the photogenerated holes travelled through the p-n heterojunction interface from TiO<sub>2</sub> VB to NiO VB thus establishing efficient charge separation. The holes in NiO VB directly engaged in H<sub>2</sub>O oxidation reaction to produce O<sub>2</sub> gas while H<sub>2</sub> is produced at the Pt cathode. Second for Au<sub>y</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs photoanodes (Fig. 13); it was proposed that Au nanoparticles were photo-deposited on the surface of NiO forming Schottky barrier at the Au/NiO interface. Visible light excitation activated the (LSPR) effect which led to enhanced light harvesting and hot electron generation in the plasmonic Au nanoparticles. The hot electrons overcome the Schottky barrier and migrated to the CB of NiO then through the p-n heterojunction interface to the CB of TiO<sub>2</sub> where it was transferred to the cathode. Accordingly, further improvement in the charge separation efficiency and higher photocurrent densities were obtained due to the favorable synergism between the p-n heterojunction and LSPR effects.

## 4. Conclusion

A series of Ni<sub>x</sub>/TiO<sub>2</sub>NTs and Au<sub>y</sub>/Ni<sub>x</sub>/TiO<sub>2</sub>NTs photoanodes were prepared and its activity toward photoelectrochemical water-splitting for H<sub>2</sub> production under simulated solar light was investigated. A correlation was found between the photoanodes performance and the number of electrodeposition cycles and duration of photoreduction of gold. The photocurrent density was increased in the order Ni<sub>3</sub>/TiO<sub>2</sub>NTs < Ni<sub>5</sub>/TiO<sub>2</sub>NTs < Ni<sub>10</sub>/TiO<sub>2</sub>NTs < Ni<sub>20</sub>/TiO<sub>2</sub>NTs ≈ Ni<sub>30</sub>/TiO<sub>2</sub>NTs. The photocurrent density of Ni<sub>20</sub>/TiO<sub>2</sub>NTs was 0.14 mA cm<sup>-2</sup> that is 1.75-fold of pristine TiO<sub>2</sub>NTs. Photodeposition of gold further boosted the OER activity of Ni<sub>20</sub>/TiO<sub>2</sub>NTs photoanode and was found to increase in the order Au<sub>120</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs < Au<sub>60</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs < Au<sub>15</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs < Au<sub>30</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs. The photocurrent density of Au<sub>30</sub>/Ni<sub>20</sub>/TiO<sub>2</sub>NTs was 0.26 mA cm<sup>-2</sup> that is 3.25-fold of pristine TiO<sub>2</sub>NTs, this enhancement was attributed to LSPR effect of nanometric gold and the synergism between Ni and Au leading to better solar light harvesting, charge separation and

transportation. This research may have significant implications for the synthesis of nanomaterials with improved light harvesting for photo- and photoelectrocatalytic applications in the future.

## Conflicts of interest

There are no conflicts to declare.

## References

- M. A. Marwat, *et al.*, Advanced catalysts for photoelectrochemical water splitting, *ACS Appl. Energy Mater.*, 2021, **4**(11), 12007–12031.
- F. Zhang and Q. Wang, Redox-mediated water splitting for decoupled H<sub>2</sub> production, *ACS Mater. Lett.*, 2021, **3**(5), 641–651.
- S. Dutta, Review on solar hydrogen: Its prospects and limitations, *Energy Fuels*, 2021, **35**(15), 11613–11639.
- A. Govind Rajan, J. M. P. Martirez and E. A. Carter, Why do we use the materials and operating conditions we use for heterogeneous (photo) electrochemical water splitting?, *ACS Catal.*, 2020, **10**(19), 11177–11234.
- S. Jin, What else can photoelectrochemical solar energy conversion do besides water splitting and CO<sub>2</sub> reduction?, *ACS Energy Lett.*, 2018, **3**(10), 2610–2612.
- P. Varadhan, *et al.*, An efficient and stable photoelectrochemical system with 9% solar-to-hydrogen conversion efficiency via InGaP/GaAs double junction, *Nat. Commun.*, 2019, **10**(1), 1–9.
- L. Deng, *et al.*, MXene decorated by phosphorus-doped TiO<sub>2</sub> for photo-enhanced electrocatalytic hydrogen evolution reaction, *Renewable Energy*, 2021, **170**, 858–865.
- B. Chang, *et al.*, Photo-enhanced electrocatalysis of sea-urchin shaped Ni<sub>3</sub>(VO<sub>4</sub>)<sub>2</sub> for the hydrogen evolution reaction, *J. Mater. Chem. A*, 2017, **5**(34), 18038–18043.
- B. Chang, *et al.*, p-n tungsten oxide homojunctions for Vis-NIR light-enhanced electrocatalytic hydrogen evolution, *J. Mater. Chem. A*, 2019, **7**(33), 19573–19580.



- 10 C. Ding, *et al.*, Photoelectrocatalytic water splitting: significance of cocatalysts, electrolyte, and interfaces, *ACS Catal.*, 2017, 7(1), 675–688.
- 11 X.-C. Lu, *et al.*, Efficient photoelectrodes based on two-dimensional transition metal dichalcogenides heterostructures: from design to construction, *Rare Met.*, 2022, 1–18.
- 12 M. S. Afify, *et al.*, Effects of Ag doping on LaMnO<sub>3</sub> photocatalysts for photoelectrochemical water splitting, *Appl. Phys. A: Mater. Sci. Process.*, 2022, 128(10), 1–12.
- 13 S. Zhang, *et al.*, Crystallographic orientation and morphology control of Sb<sub>2</sub>Se<sub>3</sub> to sensitize TiO<sub>2</sub> nanotube arrays for enhanced photoelectrochemical performances, *Chem. Eng. J.*, 2022, 429, 132091.
- 14 K. Arifin, *et al.*, Improvement of TiO<sub>2</sub> nanotubes for photoelectrochemical water splitting, *Int. J. Hydrogen Energy*, 2021, 46(7), 4998–5024.
- 15 Q. Guo, *et al.*, Fundamentals of TiO<sub>2</sub> photocatalysis: concepts, mechanisms, and challenges, *Adv. Mater.*, 2019, 31(50), 1901997.
- 16 X. Chen, *et al.*, Ultrathin tungsten-doped hydrogenated titanium dioxide nanosheets for solar-driven hydrogen evolution, *Inorg. Chem. Front.*, 2022, 9(17), 4470–4477.
- 17 J. W. Yoon, *et al.*, Heterojunction between bimetallic metal-organic framework and TiO<sub>2</sub>: Band-structure engineering for effective photoelectrochemical water splitting, *Nano Res.*, 2022, 1–8.
- 18 A. E. A. Aboubakr, *et al.*, Effect of morphology and non-metal doping (P and S) on the activity of graphitic carbon nitride toward photoelectrochemical water oxidation, *Sol. Energy Mater. Sol. Cells*, 2021, 232, 111326.
- 19 M.-Z. Ge, *et al.*, In situ plasmonic Ag nanoparticle anchored TiO<sub>2</sub> nanotube arrays as visible-light-driven photocatalysts for enhanced water splitting, *Nanoscale*, 2016, 8(9), 5226–5234.
- 20 W. M. El Rouby, *et al.*, Surface sensitization of TiO<sub>2</sub> nanorod mats by electrodeposition of ZIF-67 for water photo-oxidation, *Electrochim. Acta*, 2020, 339, 135882.
- 21 W. M. El Rouby, *et al.*, Role of photosensitizers in enhancing the performance of nanocrystalline TiO<sub>2</sub> for photoelectrochemical water splitting, *Nanoscience*, 2021, 181–212.
- 22 W. Fang, M. Xing and J. Zhang, A new approach to prepare Ti<sup>3+</sup> self-doped TiO<sub>2</sub> via NaBH<sub>4</sub> reduction and hydrochloric acid treatment, *Appl. Catal., B*, 2014, 160, 240–246.
- 23 J. Li, *et al.*, Vacancy-enabled mesoporous TiO<sub>2</sub> modulated by nickel doping with enhanced photocatalytic nitrogen fixation performance, *ACS Sustainable Chem. Eng.*, 2020, 8(49), 18258–18265.
- 24 M. H. Elbakkay, *et al.*, Highly active atomic Cu catalyst anchored on superlattice CoFe layered double hydroxide for efficient oxygen evolution electrocatalysis, *Int. J. Hydrogen Energy*, 2022, 47(17), 9876–9894.
- 25 Q. Liu, *et al.*, Black Ni-doped TiO<sub>2</sub> photoanodes for high-efficiency photoelectrochemical water-splitting, *Int. J. Hydrogen Energy*, 2015, 40(5), 2107–2114.
- 26 C.-C. Wang, *et al.*, Deposition of Ni nanoparticles on black TiO<sub>2</sub> nanowire arrays for photoelectrochemical water splitting by atomic layer deposition, *Electrochim. Acta*, 2018, 284, 211–219.
- 27 L. Yu, *et al.*, Effect of unsaturated coordination on photoelectrochemical properties of Ni-MOF/TiO<sub>2</sub> photoanode for water splitting, *Int. J. Hydrogen Energy*, 2021, 46(34), 17741–17750.
- 28 Z. Dong, *et al.*, Facile preparation of Ti<sup>3+</sup>/Ni co-doped TiO<sub>2</sub> nanotubes photoanode for efficient photoelectrochemical water splitting, *Appl. Surf. Sci.*, 2019, 480, 219–228.
- 29 S. Fang, Z. Sun and Y. H. Hu, Insights into the thermo-photo catalytic production of hydrogen from water on a low-cost NiO x-loaded TiO<sub>2</sub> catalyst, *ACS Catal.*, 2019, 9(6), 5047–5056.
- 30 Z. Dong, *et al.*, Ni-doped TiO<sub>2</sub> nanotubes photoanode for enhanced photoelectrochemical water splitting, *Appl. Surf. Sci.*, 2018, 443, 321–328.
- 31 W.-T. Chen, *et al.*, Performance comparison of Ni/TiO<sub>2</sub> and Au/TiO<sub>2</sub> photocatalysts for H<sub>2</sub> production in different alcohol-water mixtures, *J. Catal.*, 2018, 367, 27–42.
- 32 T. Elysabeth, *et al.*, Synthesis of Ni-and N-doped titania nanotube arrays for photocatalytic hydrogen production from glycerol–water solutions, *Catalysts*, 2020, 10(11), 1234.
- 33 J. Li, *et al.*, The high surface energy of NiO {110} facets incorporated into TiO<sub>2</sub> hollow microspheres by etching Ti plate for enhanced photocatalytic and photoelectrochemical activity, *Appl. Surf. Sci.*, 2017, 396, 1539–1545.
- 34 W. Hong, *et al.*, High-performance silicon photoanode enhanced by gold nanoparticles for efficient water oxidation, *ACS Appl. Mater. Interfaces*, 2018, 10(7), 6262–6268.
- 35 S. Oros-Ruiz, *et al.*, Photocatalytic hydrogen production by Au–MxOy (Mg, Cu, Ni) catalysts supported on TiO<sub>2</sub>, *Catal. Commun.*, 2014, 47, 1–6.
- 36 Z. Lian, *et al.*, Plasmonic silver quantum dots coupled with hierarchical TiO<sub>2</sub> nanotube arrays photoelectrodes for efficient visible-light photoelectrocatalytic hydrogen evolution, *Sci. Rep.*, 2015, 5(1), 1–10.
- 37 S. Y. Moon, *et al.*, Plasmonic hot carrier-driven oxygen evolution reaction on Au nanoparticles/TiO<sub>2</sub> nanotube arrays, *Nanoscale*, 2018, 10(47), 22180–22188.
- 38 Q. Wang, *et al.*, MoS<sub>2</sub> Quantum Dots@ TiO<sub>2</sub> Nanotube Arrays: An Extended-Spectrum-Driven Photocatalyst for Solar Hydrogen Evolution, *ChemSusChem*, 2018, 11(10), 1708–1721.
- 39 W. Li and T. Zeng, Preparation of TiO<sub>2</sub> anatase nanocrystals by TiCl<sub>4</sub> hydrolysis with additive H<sub>2</sub>SO<sub>4</sub>, *PLoS One*, 2011, 6(6), e21082.
- 40 W. Wong-Ng, *et al.*, JCPDS-ICDD research associateship (cooperative program with NBS/NIST), *J. Res. Natl. Inst. Stand. Technol.*, 2001, 106(6), 1013.
- 41 L. Barrientos, *et al.*, Unveiling the structure of Ni/Ni oxide nanoparticles system, *J. Chil. Chem. Soc.*, 2009, 54(4), 391–393.



- 42 S.-M. You, *et al.*, Fe/Ni Bimetallic Organic Framework Deposited on TiO<sub>2</sub>(2) Nanotube Array for Enhancing Higher and Stable Photoelectrochemical Activity of Oxygen Evaluation Reaction, *Nanomaterials*, 2020, **10**(9), 1688.
- 43 F. Liao, *et al.*, Carbon dots dominated photoelectric surface in titanium dioxide nanotube/nitrogen-doped carbon dot/gold nanocomposites for improved photoelectrochemical water splitting, *J. Colloid Interface Sci.*, 2022, **606**, 1274–1283.
- 44 S. Kumbhar, S. Shaikh and K. Rajpure, Hydrothermally-Grown TiO<sub>2</sub> thin film-based metal–semiconductor–metal UV photodetector, *J. Electron. Mater.*, 2020, **49**(1), 499–509.
- 45 R. Yalavarthi, *et al.*, Radiative and non-radiative recombination pathways in mixed-phase TiO<sub>2</sub> nanotubes for PEC water-splitting, *Catalysts*, 2019, **9**(2), 204.
- 46 L. Manuel, *et al.*, One-pot synthesis of Au/N-TiO<sub>2</sub> photocatalysts for environmental applications: Enhancement of dyes and NO<sub>x</sub> photodegradation, *Powder Technol.*, 2019, **355**, 793–807.
- 47 F. Settle, *Handbook of instrumental techniques for analytical chemistry*, 1997.
- 48 M. Hinojosa-Reyes, *et al.*, Gold-TiO<sub>2</sub>-Nickel catalysts for low temperature-driven CO oxidation reaction, *Appl. Surf. Sci.*, 2016, **368**, 224–232.
- 49 S. K. Khore, *et al.*, Solar light active plasmonic Au@ TiO<sub>2</sub> nanocomposite with superior photocatalytic performance for H<sub>2</sub> production and pollutant degradation, *New J. Chem.*, 2018, **42**(13), 10958–10968.
- 50 Y. Fu, *et al.*, XPS characterization of surface and interfacial structure of sputtered TiNi films on Si substrate, *Mater. Sci. Eng., A*, 2005, **403**(1–2), 25–31.
- 51 H. Zhang, *et al.*, Self-powered TiO<sub>2</sub> NRs UV photodetectors: Heterojunction with PTTh and enhanced responsivity by Au nanoparticles, *J. Alloys Compd.*, 2022, **899**, 163279.
- 52 D.-M. Amaya-Dueñas, *et al.*, A-site deficient chromite with in situ Ni exsolution as a fuel electrode for solid oxide cells (SOCs), *J. Mater. Chem. A*, 2021, **9**(9), 5685–5701.
- 53 S. A. Tenney, *et al.*, Characterization of Pt–Au and Ni–Au Clusters on TiO<sub>2</sub> (110), *Top. Catal.*, 2011, **54**(1), 42–55.
- 54 H. Wang, *et al.*, Effective photocatalytic properties of N doped Titanium dioxide nanotube arrays prepared by anodization, *React. Kinet., Mech. Catal.*, 2012, **106**(2), 341–353.
- 55 S. Zhang, *et al.*, Electrodeposition preparation of Ag loaded N-doped TiO<sub>2</sub> nanotube arrays with enhanced visible light photocatalytic performance, *Catal. Commun.*, 2011, **12**(8), 689–693.
- 56 E. Fudo, *et al.*, Modification of gold nanoparticles with a hole-transferring cocatalyst: a new strategy for plasmonic water splitting under irradiation of visible light, *Sustainable Energy Fuels*, 2021, **5**(13), 3303–3311.
- 57 Y. Yu, *et al.*, UV and visible light photocatalytic activity of Au/TiO<sub>2</sub> nanoforests with Anatase/Rutile phase junctions and controlled Au locations, *Sci. Rep.*, 2017, **7**(1), 41253.
- 58 W. M. El Roubi and A. A. Farghali, Titania morphologies modified gold nanoparticles for highly catalytic photoelectrochemical water splitting, *J. Photochem. Photobiol., A*, 2018, **364**, 740–749.
- 59 S. K. Mohamed, *et al.*, Facile fabrication of ordered mesoporous Bi/Ti-MCM-41 nanocomposites for visible light-driven photocatalytic degradation of methylene blue and CO oxidation, *Sep. Purif. Technol.*, 2018, **195**, 174–183.
- 60 E. M. Neville, *et al.*, Visible light active C-doped titanate nanotubes prepared via alkaline hydrothermal treatment of C-doped nanoparticulate TiO<sub>2</sub>: Photo-electrochemical and photocatalytic properties, *J. Photochem. Photobiol., A*, 2013, **267**, 17–24.
- 61 A. Talla, *et al.*, Effect of annealing temperature and atmosphere on the structural, morphological and luminescent properties of TiO<sub>2</sub> nanotubes, *Phys. B*, 2022, **414026**.
- 62 Q. Kang, *et al.*, Reduced TiO<sub>2</sub> nanotube arrays for photoelectrochemical water splitting, *J. Mater. Chem. A*, 2013, **1**(18), 5766–5774.
- 63 G. Marci and L. Palmisano, *Heterogeneous photocatalysis: Relationships with heterogeneous catalysis and perspectives*, Elsevier, 2019.
- 64 L. Lin, *et al.*, Size effect of Au nanoparticles in Au-TiO<sub>2</sub>-x photocatalyst, *Chem. Phys. Lett.*, 2021, **770**, 138457.
- 65 C. S. Yaw, *et al.*, A Type II nn staggered orthorhombic V<sub>2</sub>O<sub>5</sub>/monoclinic clinobisvanite BiVO<sub>4</sub> heterojunction photoanode for photoelectrochemical water oxidation: fabrication, characterisation and experimental validation, *Chem. Eng. J.*, 2019, **364**, 177–185.
- 66 N. Mukurala, *et al.*, Cu<sub>2</sub>FeSnS<sub>4</sub> decorated Ni-TiO<sub>2</sub> nanorods heterostructured photoanode for enhancing water splitting performance, *Appl. Surf. Sci.*, 2021, **551**, 149377.
- 67 P. Peerakiathajohn, *et al.*, Surface plasmon-driven photoelectrochemical water splitting of a Ag/TiO<sub>2</sub> nanoplate photoanode, *RSC Adv.*, 2022, **12**(5), 2652–2661.
- 68 C. Chen, *et al.*, Morphology-controlled In<sub>2</sub>O<sub>3</sub> nanostructures enhance the performance of photoelectrochemical water oxidation, *Nanoscale*, 2015, **7**(8), 3683–3693.
- 69 T. Li, *et al.*, Fabrication of n-type CuInS<sub>2</sub> modified TiO<sub>2</sub> nanotube arrays heterostructure photoelectrode with enhanced photoelectrocatalytic properties, *Appl. Catal., B*, 2014, **156**, 362–370.
- 70 W. M. El Roubi, *et al.*, Synthesis and characterization of Bi-doped g-C<sub>3</sub>N<sub>4</sub> for photoelectrochemical water oxidation, *Sol. Energy*, 2020, **211**, 478–487.
- 71 M. Zhang, *et al.*, AgInS<sub>2</sub> nanoparticles modified TiO<sub>2</sub> nanotube array electrodes: Ultrasonic-assisted SILAR preparation and mechanism of enhanced photoelectrocatalytic activity, *Mol. Catal.*, 2017, **442**, 97–106.
- 72 S. Huo, *et al.*, Core-shell TiO<sub>2</sub>@ Au<sub>25</sub>/TiO<sub>2</sub> nanowire arrays photoanode for efficient photoelectrochemical full water splitting, *Ind. Eng. Chem. Res.*, 2020, **59**(32), 14224–14233.
- 73 X. Shi, *et al.*, Plasmon-enhanced photocurrent generation and water oxidation with a gold nanoisland-loaded titanium dioxide photoelectrode, *J. Phys. Chem. C*, 2013, **117**(6), 2494–2499.
- 74 N. Celebi, *et al.*, Ligand-free fabrication of Au/TiO<sub>2</sub> nanostructures for plasmonic hot-electron-driven





- photocatalysis: Photoelectrochemical water splitting and organic-dye degradation, *J. Alloys Compd.*, 2021, **860**, 157908.
- 75 Y. Zhang, *et al.*, Surface plasmon resonance metal-coupled biomass carbon modified TiO<sub>2</sub> nanorods for photoelectrochemical water splitting, *Chin. J. Chem. Eng.*, 2022, **41**, 403–411.
  - 76 S. Wang, *et al.*, Defective black Ti<sub>3+</sub> self-doped TiO<sub>2</sub> and reduced graphene oxide composite nanoparticles for boosting visible-light driven photocatalytic and photoelectrochemical activity, *Appl. Surf. Sci.*, 2019, **467**, 45–55.
  - 77 W. Wang, *et al.*, Photoelectrocatalytic hydrogen generation and simultaneous degradation of organic pollutant via CdSe/TiO<sub>2</sub> nanotube arrays, *Appl. Surf. Sci.*, 2016, **362**, 490–497.
  - 78 H. Yu, *et al.*, Fabrication of a stable light-activated and p/n type AgVO<sub>3</sub>/V<sub>2</sub>O<sub>5</sub>-TiO<sub>2</sub> heterojunction for pollutants removal and photoelectrochemical water splitting, *J. Alloys Compd.*, 2022, **894**, 162500.
  - 79 Z. Xiao, *et al.*, Preparation of GQDs/TiO<sub>2</sub> nanotube heterojunction photoanode and its photoelectrochemical performance for water splitting, *Int. J. Electrochem. Sci.*, 2022, **17**(220817), 2.
  - 80 M. M. Momeni, *et al.*, Preparation of chromium and sulfur single and co-doped TiO<sub>2</sub> nanostructures for efficient photoelectrochemical water splitting: effect of aliphatic alcohols on their activity, *J. Solid State Electrochem.*, 2022, **26**(1), 281–291.
  - 81 N. Khatun, *et al.*, Ti<sub>3</sub>C<sub>2</sub>T<sub>x</sub> MXene functionalization induced enhancement of photoelectrochemical performance of TiO<sub>2</sub> nanotube arrays, *Mater. Chem. Phys.*, 2022, **278**, 125651.
  - 82 Z. Zhang, *et al.*, Plasmonic gold nanocrystals coupled with photonic crystal seamlessly on TiO<sub>2</sub> nanotube photoelectrodes for efficient visible light photoelectrochemical water splitting, *Nano Lett.*, 2013, **13**(1), 14–20.

