

Materials Advances



Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: N. Callaghan, C. A. Rempe, Z. Froom, K. Medd and L. Davenport Huyer, *Mater. Adv.*, 2024, DOI: 10.1039/D4MA00333K.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the <u>Information for Authors</u>.

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard <u>Terms & Conditions</u> and the <u>Ethical guidelines</u> still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.



Cell dynamics and metabolism of the foreign body response: characterizing hostbiomaterial interactions for next-generation medical implant biocompatibility

Neal I. Callaghan ^{1#}, Christian N. Rempe^{2#}, Zachary Froom ³, Kyle Medd ³, Locke Davenport Huyer ^{2-5*}

- ¹ Faculty of Medicine, Dalhousie University, Halifax, NS B3H 2Y9, Canada
- ² Department of Microbiology & Immunology, Faculty of Medicine, Dalhousie University, Halifax, NS B3H 4R2, Canada
- ³ School of Biomedical Engineering, Faculties of Medicine and Engineering, Dalhousie University, Halifax, NS B3H 4R2, Canada
- ⁴ Department of Applied Oral Sciences, Faculty of Dentistry, Dalhousie University, Halifax, NS B3H 4R2, Canada
- ⁵ Nova Scotia Health, Halifax, NS Canada

Keywords: fibrosis, medical devices, immune, macrophage, granuloma, giant cell, immune evasion, polymer

- # Contributed equally to work
- * Correspondence to: l.davenporthuyer@dal.ca

Abstract

Implantable medical devices (IMDs) collectively represent a critical mainstay in modern medicine. Used in many chronic diseases and in acute surgical interventions, IMDs are often associated with improvements in disease progression, quality of life, and mortality rates. Despite the positive impacts of IMD implementation, excessive fibrosis driven by the foreign body response (FBR) is frequently associated with the development of complications and failure. These complications in turn result in surgical revisions and removals, which represent a significant burden to healthcare costs and surgical wait-times in countries with elevated IMD usage rates. IMD complications are exacerbated by limitations to treatment options and limited availability of biocompatible materials. Novel treatment development is equally hampered by the complexity of the FBR, wherein complex cellular behaviors defy canonical immunological classification systems. In this review, current understandings of cellular dynamics and kinetics within the FBR are summarized, with a specific focus on the relationship between immunometabolic regulation and pathological fibrotic processes across various cell behaviours in the FBR. This review also explores promising emerging *in vitro* and *in vivo* techniques of FBR characterization, and highlights biomaterial properties associated with alterations in FBR outcomes. Finally, this review explores current and future approaches to biocompatible material development, highlighting immune-metabolic control as a therapeutic approach to mitigating the FBR.

1. The foreign body response to implanted materials: burden and

clinical implications

Implantable medical devices (IMDs) have broad utility in the medical field, with applications spanning sutures, structural meshes, soft tissue fillers, orthopedic and craniofacial prosthetics, cerebral shunts, vascular stents, valvular prostheses, cardiac and neural stimulators, biosensors, contraceptive devices, and long-term drug eluting devices. For example, the single most common surgical procedure is the repair of primary or incisional ventral hernia, which is a prototypical example of soft tissue implant; current USA caseloads are approximately 611 000 per year and with a total cost of \$9.7 billion USD ¹. When combined with inguinal and femoral hernias, the incidence of medically significant cases remain undertreated, with combined incidence of approximately 13 million cases per year and representing a major source of morbidity, mortality, complications, and recurrence, as well as a significant component of healthcare spending ^{2,3}. With an aging population in the Western hemisphere and increased medical spending, along with continuous surgical innovation and the release of new IMDs, rates of surgical implantation are projected to increase for the foreseeable future.

Generally, IMDs positively impact recipient quality of life (e.g., hernia repair via a polypropylene surgical mesh), but also carry complication risks ⁴. Specifically, IMDs are generally subject to some degree of chronic inflammation associated with the foreign body response (FBR) to implanted materials. The FBR is an expected inflammatory reaction, mediated by the immune system, that arises following implantation of a biomaterial within a host organism ⁵, and that is characterized by the persistence of immune cells and the development of a fibrotic layer encapsulating and isolating the implant ^{6,7}. Based on patient, implant, and environmental factors, the FBR can manifest on a spectrum of severity. The FBR in a successful medical device application may present with no discernable impact on device function or patient quality of life. Conversely, a deleterious FBR can completely impair device function, severely incapacitate patients with pain or reduced quality of life, leads to systemic sequelae, or even threatens patient life altogether ⁴. This pathology is characterized by a prolonged period of chronic inflammation, and the deposition of fibrotic matrix around the implant to isolate the area from prolonged tissue damage. This damage results from inflammatory molecules secreted by the immune system; generally, the more prolonged the inflammation resulting from implantation, the thicker the eventual fibrosis will be ⁵. However, the immune system is also a powerful driver of tissue growth and healing, and in the future will likely be directly manipulated and harnessed in regenerative approaches ⁸.

Despite the clinical ubiquity of IMDs and their respective complications, the mechanisms underlying the FBR are poorly understood. It is accepted that primary drivers of the FBR include chronic inflammation and the pathological recruitment of a variety of myeloid cells ⁹ (**Figure 1**). These cells drive excess fibrosis and limit tissue integration of the implant ⁹. Typically, pathological inflammation and fibrosis manifests clinically as capsular contracture, resulting in pain and in extreme cases alteration of an implant's structure; symptoms may require surgical revision or explantation. Additionally, pathological fibrosis can interfere with implant function. For example, fibrotic depositions can alter drug elution rates in insulin delivery devices ¹⁰, or implanted electrode function ^{11–13}. Though clear clinical complications are associated with pathological FBR fibrosis, the complement of involved cells, their activators and regulators, and their correlation to the final disposition of the FBR remain undercapitalized. More rare adverse outcomes can include the development of autoimmune diseases (e.g., breast implant illness) and even malignancy; these are generally thought to be result from prolonged local or systemic immunostimulation, but their study is hampered by little direct clinical study or model development ¹⁴.

In this review, we discuss the mechanisms of the FBR, with focus on the dynamics and metabolism of participating cells in the peri-implant environment and in environments out of direct contact with systemic circulation. We review recent literature that elucidates the provenance of these cells, and the checkpoints that mediate inflammatory resolution and implant integration, or alternatively lead to chronic inflammation. Finally, we discuss novel scientific

advancements in the techniques that query patient explants and *in vivo* and *in vitro* models of the FBR, as well as metabolically-based solutions to the FBR and associated pathology.

2. Physiology of the foreign body response

The most harmonious explanation for the physiological utility of the FBR is twofold: the rapid repair of the wounded tissue including protection from the external environment, and the neutralization and sequestration of both active and latent pathogens introduced with the foreign body. The placement of an IMD generates a wound environment, including significant tissue damage, and thus drives signaling of canonical wound repair processes. In models of incisional skin wound healing (arguably the most studied of tissue wound healing processes), the first week of healing is characterized by a hemostatic plug that allows for inflammatory cell infiltration and sterilization, but imparts minimal tensile strength to the wound closure. This strength greatly increases in the second week, and progresses over the course of further weeks to months to a plateau of ~80% of normal dermis ^{15,16}. At a fundamental level, the FBR can be considered in the context of the wound healing paradigm, and the mechanistic drive for wound closure.

Early phases of wound healing utilize inflammatory pathways to eliminate damaged tissue, and address pathogens in the microenvironment. Pathogen exposure is a minimizable but unavoidable consequence of material implantation, and attributable to both endogenous (patient-colonizing) and exogenous sources (airborne particles in the operating room, films or particles from IMDs, surgical tools, and operators) ¹⁷. Considering abdominal wall hernia repair meshes as an example, surgical site infection occurrence rates range enormously depending on wound and mesh size, mesh characteristics, surgical technique, environment, prophylaxis, dressing, and active wound management, as well as patient demographic factors ^{17–25}. The development of a fibrous barrier allows for spatial limitation of pathogen growth, as well as the protection of surrounding tissue from the cytotoxic anti-pathogen response from infiltrating immune cells during the FBR.

When considering the utility of implantable devices in surgical techniques, the FBR is critical for implanted materials to achieve stability in tissue and carry out their functional roles. The utility of controlled fibrosis increasing tissue hardness and stiffness is especially crucial in the face of recent medical devices. In the context of hernias, mesh repairs generally outperform non-mesh repairs in rate of primary recurrence ^{26–28}, generally attributable to the increased fibrosis at and around the surgical mesh; this supraphysiological stiffness of the mesh and hypertrophic scar tissue together allow for sufficient integration and tensile strength to ensure patency. Similarly, in silicone breast reconstruction, fibrosis is required for successful tissue integration and implant stability to minimize risk of displacement ^{4,29,30}. Without the FBR, implantable medical devices of all designations would be at risk for dislodgement and loss of function or even active pathology.

However, careful attention to detail is warranted in considering tissue and IMD mechanics. For example, the adaptation of polymer meshes originally designed for use in abdominal wall hernias for gynecological application in pelvic floor dysfunction, specifically in the adoption of transvaginal meshes, has been met with significant rates of complications ³¹. These generally result from both differential elasticity under deformation between native tissue and the implanted material. As implantable meshes plastically deform, their interaction with softer surrounding native tissues often leads to erosion, which is often complicated by chronic pain, infection, dyspareunia, and autoexplantation or extrusion leading to perforation of surrounding organs, prolapse recurrence, or excess fibrosis ³¹. These complications occur much more frequently in the gynecological setting than the original abdominal wall setting, leading to widespread cancellation of medical device approvals by regulatory agencies, and the ongoing tempering of their recommendations by professional medical societies ^{32–34}. This differential outcome between the use of similar devices for different indications underscores the importance of application specific considerations (i.e. microenvironmental signaling and mechanics) in designing surgical solutions. To understand the factors underlying these critical mechanics of the host-wound interface, a thorough understanding of relevant biology is warranted.

90 91

92

93

94

95

96

97

98

99 100

101

102

103

104

105106

107

108

109 110

111

112

113 114

115

116 117

118

119

120

121

122123

124

125

126 127

128

129 130

131

132

133

2.1. Timeline of the foreign body response

Placement of an IMD induces a wound healing response, wherein the device is placed in an environment of tissue damage. After the initial abrasion is created, and the implant is introduced into the body, an adsorption period begins 5, during which host proteins, extracellular matrix (ECM) and cell debris adsorb and desorb fluidly at the surface of the implant ⁷. Due to the tissue damage associated with implantation, adsorption occurs effectively immediately (i.e., reaching adsorbed homeostasis under 30 min) to an implant surface 35. The damaged tissues and denatured proteins surrounding the implant serve as damage-associated molecular patterns (DAMPs), which engage the cells of the immune system through pattern recognition receptors (PRRs) to respond to tissue damage ³⁶. Common DAMPs include ECM proteins such as fibrinogens, fibronectin and heparan sulfate, all of which initiate immune signaling through toll like receptor (TLR) 4 ^{37–39} as well as intracellular components (DNA, RNA, histones, etc.) ⁴⁰ and absorbed immune proteins such as complement elements and antibodies 7. Proteins adsorbed at the surface of the implant promote the recruitment of platelets, induction of complement cascading, and immune cell chemotaxis through cytokine signalling 36. Receptor-binding to TLRs underlies early inflammation through induction of inflammatory mediators such as IL-6 and interferons, and appropriately each TLR recognizes a finite number of ligands. Differential conformation and adsorption profiles of DAMPs may be an important factor in the inflammatory profiles associated with different materials 41. In the FBR, adsorbed DAMPs (namely fibronectin and fibrinogen) have implicated both TLR2 & TLR4 as activating PRRs ^{6,42} with downstream activation of NF-κB and pro-inflammatory mediators. However, the breadth of DAMP signalling engaged during the FBR likely involves other endogenous ligand-binding TLRs (e.g., TLR3, TLR7 and TLR9) and C-type lectin receptors ³⁶. Ultimately, more research is required to identify the entirety of PRRs engaged during the FBR.

As soon as biochemical absorption has occurred, cell reaction local to the foreign body induces resident immune cell activation and recruitment of more distal or systemically circulating immune cells. These events constitute the acute inflammatory phase of the FBR, lasting for hours to days 5 and characterized by nonspecific cell activity optimized for rapid neutralization of invading organisms and systemic immune escalation and recruitment (Table 1). Neutrophils are the 'first responders' of the FBR and secrete pro-inflammatory cytokines 5,7,36. Neutrophil extracellular trap (NET) activity, reactive oxygen species (ROS) production and chemoattractant production are also induced by neutrophils 5,7,36. To date, the balance of evidence suggests key roles of these functions in 43-45 in propagating deleterious FBRs, although differences may be minimal or only manifest later in the course of healing and fibrosis ^{43–4546}. Additionally, mast cells have long been recognized as critical to the early FBR, as well as to the fibrotic process; early mast cell degranulation is ostensibly responsible for neutrophil and monocyte extravasation and chemotaxis to the peri-implant environment in the context of the FBR ^{47,48}. The mast cell response, although somewhat lacking in recent study, has been linked specifically to near-instantaneous fibrinogen binding and activation on the surface of implanted biomaterials ⁴⁹, with modulation of this pathway robustly affecting the early response with a negligible to moderate effect on fibrotic outcome 38,47,48. Despite long-standing knowledge, mechanistic study of mast cell contributions to the FBR have been hampered by challenges associated with in vitro study and in modulating the mast cell response experimentally in vivo 50.

The release of inflammatory mediators during the acute inflammatory phase contributes to the recruitment of macrophages, critically involved in the FBR ^{5,7,36}; the continued recruitment of these cells and persistence beyond that of mast cells and neutrophils, and forms the *chronic phase* as specific to the field of biomaterials and the FBR ^{5,51}. Macrophages, in turn, respond to DAMPs associated with the implant surface through secretion of inflammatory molecules ^{5,7,36,52}. During normal wound healing processes, inflammatory macrophages are short-lived. This is in contrast with macrophages in the FBR, which remain inflammatory due to the persistence of the implant and denatured proteins within the host. In the absence of foreign material, this chronic phase gives way to a resolution phase; continued exposure to foreign material instead induces granulation in the *FBGC formation phase*, which will be discussed below.

 To protect the body from the harmful products being released by immune cells that direct the chronic inflammatory response at the implant interface, macrophages secrete pro-fibrotic cytokines, and recruit fibroblasts which deposit a collagenous layer of tissue around the implant ^{5,7,36,52}. This collagenous layer is referred to as the fibrotic capsule. The fibrotic capsule plays a critical role in determining the negative outcomes of the FBR, including discomfort, pain, capsular contracture and implant failure ⁴. This process of fibrotic encapsulation and ongoing immune reaction at the implant-interface constitute the final phase of the FBR, the *fibrous capsule* phase ^{5,7,36,52}. As the capsule continues to form, a variety of pro-inflammatory macrophage- and FBGC-secreted cytokines, in particular vascular endothelial growth factor (VEGF), mediate angiogenesis and recruitment/activation of myofibroblastic processes ⁹. Finally, although the formation of a foreign body granuloma does not require adaptive immunity ⁵³, adaptive immune cells (i.e., lymphocytes) are present in large quantity in local region ^{43,54,55}. There is currently little evidence to support direct antigenicity of synthetic polymeric biomaterials, but FBRs have featured T- and B-cells interacting either directly with biomaterials or in response to macrophage secretions, and then acting as intermediaries and amplifiers to cytokines and chemokines by other cells ^{54,56–59}.

Macrophage phenotypes associated with the foreign body response

2.2.1. Canonical macrophage classification systems

The canonical classification system for macrophages is the M1/M2 paradigm, wherein M1 macrophages are considered pro-inflammatory or classically activated, and M2 macrophages are considered pro-reparative or alternatively activated ^{60,61}. The role of M1 vs. M2 macrophages in directing inflammation and its resolution has been excellently profiled elsewhere ⁶²; classical activation generally results from stimulation with lipopolysaccharide (LPS) and interferon (IFN)y, which is associated with pathogen and damage clearance ⁶³. Phenotypically, M1 macrophages are characterized by elevated MHC-II and CD-80/CD-86 expression, indicative of antigen presentation and costimulatory T-cell activation respectively ⁶³. Generally, alternative activation results from stimulation with reparative cytokines such as IL-4, IL-13 and IL-10, and M2 macrophages are involved in tissue remodelling and debris clearance ^{63,64}. Phenotypically, M2 macrophages are generally identified as expressing CD-206 (or the macrophage mannose receptor) ⁶³, however the M2 grouping of macrophages is diverse. A plethora of stimulating factors inducing the expression of a variety of phenotypic markers has resulted in the generation of subgroups for specification of cellular behaviors known collectively as M2.

There is an increasingly pervasive skepticism towards this classification system however, particularly in the context of complex environments like the FBR, as focused investigation reveals that macrophage phenotypes have indicated a greater number of exceptions to the M1/M2 rule than not ^{60,61,65}. In the tissue-implant microenvironment, macrophages show elements of both M1 and M2, due to their involvement in inflammation and remodelling ⁶⁵; this may help to explain the generally-accepted observation that a "runaway" M2 response is considered to be a contributor to the pro-fibrotic component of the FBR. Macrophages may first require inflammatory activation to develop a robust M2-like response, which may contribute to this phenotype in the chronic inflammatory environment of fibrosis ⁶⁶. Oversimplification of macrophage subsets is further complicated by heterogeneity in phenotypes in the fibrotic tissue microenvironments; macrophages of both characteristic phenotypes that may be arranged in a spatially distinct fashion, contributing to the macroscopic phenotype of the environment ⁶⁷.

Further nuance can be attributed to tissue-specific macrophage metabolic preferences in inflammation ⁶⁸, findings of systemic immunity or its interactors (e.g. gut microbiome) influencing the response to implanted materials ⁶⁹, and findings that various macrophages functions (e.g., secretion of individual cytokines) seem dependent on different metabolic pathways and again differential per activation profile ⁷⁰. Efforts to establish an FBR-specific macrophage

178

179

180

181 182

183

184

185

186

187 188

189

190

191

192

193

194

195

196

197

198

199

200

201

202203

204

205

206 207

208

209

210

211212

213

214215

216217

218

219

220221

phenotype are progressing, although clear models of function remain challenged by discrepancies between different experimental models and techniques 71 . In the FBR, macrophages produce pro-inflammatory cytokines 72 such as Tumor Necrosis Factor (TNF), interleukin-6 (IL-6), and interleukin-1 β (IL-1 β) as well as pro-reparative cytokines such as Transforming Growth Factor β (TGF β), leading to speculation that macrophages in this environment might represent a novel phenotype, ill-defined by the M1/M2 system 60,61,65 , but characterized by an environment rich in IL-4, IL-17, and IL-34 59,73 .

2.2.2. Correlating function to metabolic macrophage phenotypes

In service of better defining macrophage functional phenotype, increased effort has been focused on understanding the metabolic foci that enable domains of macrophage activity 74. The general relationship between macrophage cellular function and metabolic behavior is well established: typically, 'inflammatory' macrophages rely on glycolysis and 'reparative' macrophages rely on oxidative phosphorylation 75. Glycolytic macrophages in the early wound environment are marked by upregulated HIF1 α expression and stabilization. These cells are enriched for SLC2A1 (encoding GLUT1), as well as the expression of pro-inflammatory and pro-angiogenic genes, implicating the functionality of early wound macrophages in organizing vasculature and wound sterilization 76. These differences are functional: at the most surface level, inflammatory macrophages tend towards glycolysis as it facilitates the rapid production of ATP, without the taxing need for mitochondrial biogenesis. However, the factors linking glycolysis and inflammation are more intricate. M1 macrophages result from stimulation with LPS and IFN-y. LPS is an inducer of the NOX2 pathway, which in turn yields NADPH, critically utilized by phagocytic cells to meet the reactive oxygen species (ROS) requirement of the phagosome. Induction of this pathway has been demonstrated to require stabilization of HIF1 α by succinate accumulation, itself enabled by the TCA cycle arrest characteristic of glycolytic reprogramming. The glycolytic inhibitor 2-deoxyglucose (2-DG) has been known to negatively impact induction of the NOX2 pathway and the associated production of NADPH in LPS-stimulated macrophages 77 . HIF1 α more generally serves as a transcriptional regulator of a variety of inflammatory and glycolytic genes, serving as the best example of the overlap between glycolytic programming and inflammatory gene induction. HIF1 α suppression has been demonstrated to reduce NLRP3 inflammasome activity and IL-1β signaling in alveolar cells following bleomycininduced lung injury, linking inflammation and glycolysis, specifically within in the context of NLRP3 and woundhealing 78. The NLRP3 inflammasome is closely linked to aggressive anti-pathogen functionality in macrophages 79,80, and in the context of the FBR its inhibition can attenuate both inflammation and fibrosis 72. A growing body of evidence suggests that NLRP3 is metabolically regulated through glycolytic metabolites, TCA intermediates (including succinate, itaconate, and fumarate), and both saturated and unsaturated fatty acids 79-81. However, the precise mechanisms of these regulatory controls remain ambiguous due to differences between studies in knockout design, in vitro vs. in vivo experimentation, cell type, and the inherent pleiotropic roles of many such metabolites.

In contrast, 'reparative' (i.e., M2) late stage wound healing macrophages are putatively characterized by intact TCA cycles (OXPHOS metabolism), associated with reduced ROS production ⁸². These cells can utilize glycolysis to generate succinate as fuel for the TCA cycle, but have demonstrated the ability to maintain TCA cycle usage during glycolytic inhibition, likely through increased reliance on fatty acid oxidation (FAO) ⁸³. These changes are once again functional. Reparative macrophages are not as reliant on rapid energy turnover and the availability of synthetic intermediates, and as such do not require upregulated glycolysis and PPP to the same degree as inflammatory cells. FAO, which is notably increased in 'M2' macrophages, is typically associated with longer cellular lifespans, which would be useful in orchestrating prolonged periods of tissue remodeling.

Additionally, reparative signals and oxidative phosphorylation are linked. Various studies have pointed to the reduction in OXPHOS following IL-10 suppression, pointing to IL-10 as having a role in metabolic orchestration. Induction of these metabolic pathways are believed to contribute to the synthesis of wound-healing intermediates such as collagen ⁸⁴. IL-10 supports successful wound healing, and has been documented as anti-fibrotic by acting on

 myofibroblasts to reduce collagen gene expression and lower α -SMA production ⁸⁵. Conversely, other studies have indicated reductions in IL-10 signaling following OXPHOS interruption, suggesting that there is reciprocity to the regulation of IL-10 on OXPHOS ⁸⁶. Mechanistically, these pathways are still unclear. Further, the precise metabolic distinctions between M2 subgroups remain ambiguous. For example, the M2b subgroup of macrophages are implicated in "M2-mediated inflammation", and as such it is unlikely that these cells rely on anti-inflammatory OXPHOS and FAO pathways to the same extent as M2a macrophages, which are more strongly implicated in tissue remodeling. A 2023 publication demonstrated the capacity for strong HIF1 α associated glycolytic reprogramming of dually IL-4- and IL-13- stimulated macrophages. Though these cells showed glycolytic upregulation and succinate accumulation characteristic of M1 metabolic programming, they also maintained certain metabolic and phenotypic features characteristic of the M2 lineage, namely arginase 1 (Arg1) activity ⁸⁷. This study is useful in illustrating the potential incongruence between classification by metabolic behavior and canonical phenotyping.

Critically, within the context of the FBR, the phenotypic characteristics of macrophages are ill-defined, and reliable information regarding the metabolic behavior of these cells is even more evasive. Thus, any inferences with regards to the metabolic behavior of macrophages during the FBR are speculative and require further demonstration. However, the engagement of key cellular pathways during the FBR may shed light on the metabolic behavior of macrophages during this reaction. For example, NLRP3 inhibition has been observed to reduce implant-associated fibrosis following nerve-injury in mice 72 . The links between NLRP3 inflammation, IL-1 β expression, and glycolysis would implicate glycolysis in the chronic inflammation associated with implants. The role of glycolysis in the FBR is also supported by the high-flux HIF-1 α -mediated glycolytic metabolism observed in early wound-healing macrophages, though the persistence of HIF-1 α signaling in chronic FBR tissues remains to be demonstrated 37,76 -.

Though the induction of TGF- β signaling by implant-associated macrophages is universally believed to play a key role in the pathology of the FBR 5 , the cellular populations responsible for excessive TGF- β signaling in the FBR remain unclear 88 . This is potentially once again attributable to the cells in the FBR displaying phenotypic plasticity, with 'M1'-like cells and 'M2'-like cells being equally implicated in TGF- β signaling. Interestingly, despite being largely attributed to 'M2'-like cells (which are primarily oxidative), HIF-1 α upregulation has been shown to induce TGF- β production by human macrophages 89 , and specifically has a documented supporting role in TGF- β mediated transcription of fibrotic genes by alveolar macrophages during bleomycin-induced lung fibrosis in mice 90 . This could imply a relationship between hypoxia, glycolysis and fibrosis, though metabolic differences between the macrophage phenotypes studied would require confirmation in the FBR context. Adding further complexity, IL-10 has been observed to reduce TGF- β production by alveolar macrophages, and ultimately reduce bleomycin-induced lung fibrosis, despite the commonly held belief that both of these cytokines stem from the same cellular origins 91 . Ultimately, further analyses are required to determine the links between metabolism and excessive TGF- β signaling.

Finally, classification of macrophages in the FBR is further impaired by their formation of foreign body giant cells (FBGCs). FBGCs are large, terminally differentiated, multinucleated cells with poor phagocytic, and enhanced lysosomal abilities, suggesting a role in debris clearance and extracellular degradation; they are the hallmark of the FBR, and persist at the tissue-implant interface for the remainder of the implant life cycle 5,7,36,52 . Multiple studies have demonstrated functional roles for IL-4 and IL-13 in macrophage fusion and FBGC formation through the upregulation of mannose receptors 7,92,93 , but the exact mechanisms and conditions through which macrophage fusion occurs in the FBR are still relatively unclear. The functional role of FBGCs, however, primarily involves extracellular degradation and phagocytosis, two processes which are strongly linked to glycolysis through HIF1 α , though this link requires further study.

2.3. Foreign body giant cells

The hallmark histologic feature of the FBR is the persistent presence of both macrophages and the multinucleated giant cell (MNGC) or FBGC, the latter of which are optimal for the phagocytosis and breakdown of large particles (e.g., 45 µm or even larger ⁹⁴) that eclipse the capability of macrophages. There are multiple types of MNGC in the human body, which can be differentiated both by mechanism of formation as well as function or profiling. The best-characterized MNGs are arguably osteoclasts (mediating physiological bone remodeling in pathogen-free local environments) and Langhans giant cells (mediating granuloma formation in the presence of persistent and recalcitrant microbes such as *M. tuberculosis* and *M. leprae* as well as Bacillus Calmette-Guérin (BCG) vaccine) ⁹⁵. FBGCs are poorly-characterized in contrast to these other cell types, but have been positively identified due to different cytoplasmic structure and function as distinct from both osteoclast and infectious granulomatous MNGCs ⁵³. FBGCs have emerged as key mediators of the acute and chronic FBR with wide-ranging sensing and activity ⁹⁶, including demonstrated roles in extracellular degradation via protease excretion, large particle phagocytosis, chemokine and cytokine release for immunomodulation, and antigen presentation ^{6,7,95,97–100}.

Despite longstanding awareness of the existence of FBGCs, little is known about both their formation and their resolution. Consensus from both *in vivo* and *in vitro* study, including *in vitro* fusion protocols and microscopic and molecular evidence, strongly supports the fusion of macrophages as the major factor in MNGC formation ^{94,99–103}. However, a recent study suggested that pattern recognition receptor-induced polyploidy and frustrated mitosis were the major drivers of MNGC formation in a model of BCG granulomatosis ¹⁰⁴; these mechanisms would merit further investigation in a model of sterile granuloma such as the FBR. In the case of material implantation specifically, foreign body MNGCs are induced by IL-4 and IL-13 ^{94,99,103} secreted ostensibly from a non-T-cell source ¹⁰⁵ and aspects of this activity have been recapitulated in vitro ^{42,106}, although the precise mechanism at play and co-stimulators *in vivo* are unclear ⁹⁶. It is equally noteworthy that while mast cells are well-documented producers of IL-4 and IL-13 ¹⁰⁷, macrophage fusion has been documented following implantation in mast-cell deficient mice, further complicating the understanding of fusion signals resulting in FBGC formation ¹⁰⁸.

Biomechanical signaling has also been implicated via various integrins ^{7,100,102,109} and TRPV4-sensed stiffness ¹¹⁰ in combination with soluble cytokines ¹¹¹, which represent potential control points for improving implant biocompatibility. Additionally, TLR-mediated detection of adsorbed self proteins (i.e., DAMPs) ^{7,42,112,113} is correlated with GC formation or function. Again in the context of an infectious granuloma, complement opsonization (e.g., C3) is a potent trigger for MNGC function ⁹⁴; FBGCs may retain this activity, which could even be elicited in the context of non-opsonization sterile complement adsorption to protein-naïve biomaterial surfaces as part of the protein corona during the tissue damage associated with implantation, and so alter the course of the FBR and the material-specific safety profile ^{7,100,114}. T-cell contributions to FBR development and MNGC formation have been noted in both infectious (e.g., tuberculosis and parasite) and autoimmune pathology ⁵³. T-cell antigen response may be observed in certain instances of foreign body introduction, such as chronic beryllium disease, but other reactions such as silicosis have not yet demonstrated antigen-directed T-cell response beyond nonspecific pro- and anti-inflammatory helper T-cell and regulatory T-cell involvement ⁵³.

Many MNGCs display aspects of both M1 and M2 between function and metabolic phenotype ¹¹⁵. One mechanism might be macrophage plasticity, in which classically-activated ("M1") macrophages become resistant to TLR signaling and limit their pro-inflammatory activity while maintaining anti-inflammatory IL-10 release ¹⁰⁰. This complements both the observation that FBGCs develop after high proportions of M1 cells in the early FBR ⁴², and the hypothesis that pro-inflammatory macrophages may take on anti-inflammatory properties and fuse upon stimulation with IL-4, Il-13 or vitamin E or tocopherol *in vivo* ¹⁰³. Here, the TLR2 pathway frustration may be synergistic or even priming to cytokine-mediated transdifferentiation and cell fusion ¹¹⁶. Fibrinogen dependency of FBGC occurrence has been noted ³⁸, which correlates to mast cell degranulation during introduction of the material ⁴⁸. Material properties have long been known to influence FBGC activity, density per unit area, and ploidy ¹¹⁷. Given the context dependence on the varied functionalities of FBGCs (including cytokine secretion, phagocytosis, and enzyme secretion), it is likely

difficult to directly correlate FBGC frequency *in situ* to the ultimate outcome of an implant across conditions. Instead, the trajectory of cell function likely remains the gold standard by which to assess the relevance of FBGC presence to FBR course.

2.4. Clinical models of macrophage and giant cell function and dysfunction: the placenta and infectious vs. non-infectious granulation

Complexities of correlating histological occurrence to tissue function notwithstanding, macrophage and GC presence have long been correlated to chronic inflammation and disease outcomes based on their persistence and density. Given their often deleterious roles in pathological FBR occurrences, it is understandable that there is considerable effort to better understand the factors that mechanistically underly GC occurrence and resolution to allow for design of materials that minimize these factors of the FBR and thus improve clinical outcomes ^{113,118,119}. Therefore, additional insight in GC formation, persistence, and resolution may be found in the physiological and pathological models of the placenta and sarcoidosis, respectively.

The placenta is a high-throughput fetal-maternal interface for the exchange of dissolved O₂, nutrients, and waste, forming from the embryonic trophoblast. It primarily shields the mother from the fetus to prevent development of anti-fetus immunity, although it also restricts certain antibody classes and cell-mediated immunity. This shielding often breaks down in the presence of previous RhD antigen alloimmunization, but generally is of exceptionally high quality. Of note, the placenta features a high concentration of GCs ¹²⁰. As in the FBR, M1 and M2 distinctions break down in the placenta. There appears to be a time course of dominant signatures, but there remain both M1 and M2 markers throughout the course of normal pregnancy, and both molecular signatures and function of both M1 and all M2 subtypes persist in the healthy placenta across all stages of pregnancy ^{120,121}. M1 markers are more strongly expressed in the first trimester and aid in implantation before M2 markers demonstrate a receptivity to trophoblast invasion, vascularization, and placental development ¹²¹. Later in pregnancy, high M1 activity is correlated with preeclampsia ^{120,122}, drawing similarities to sustained inflammation and systemic sequelae in sterile FBR-related illness.

In response to infectious insults, granulation can often be effective at indefinitely sequestering an agent, or even eliminating it completely and resulting with a sterile granuloma. In contrast, these reactions as well as sterile autoimmune reactions such as Crohn disease, sarcoidosis, vasculitides, or various hypersensitivities manifesting in granulation can progress to highly deleterious impact even based solely on mass effect and resulting tissue dysfunction ⁵³, separate from any systemic effect of chronic immune activation. In many cases, the provoking antigen or insult is never found. Further understanding of the induction, propagation, and growth of granulation processes may be highly valuable to clinical resolution of these sterile diseases as well as the FBR.

2.5. Macrophage direction of myofibroblast activity

Myofibroblasts are most responsible for maladaptive fibrotic deposition during FBR. Though direct TGF β signaling from macrophages is known to promote myofibroblast induction, macrophages participate in promoting fibrosis through many pathways ^{123,124}. Early wound macrophages release IL-6, which induces paracrine TGF β signaling in fibroblasts, and promotes differentiation into myofibroblasts ¹²⁵. IL-6 can also induce myofibroblasts directly, by promoting α -SMA via a JAK1-ERK signaling pathway ¹²⁶. PDGF, another well-documented macrophage-associated inducer of fibrosis, promotes myofibroblast activation seemingly through promoting paracrine TGF- β signaling ¹²⁷. Finally, macrophages can seemingly induce myofibroblast activity through TGF- β independent mechanisms. Specifically, RELM α expression induces α -SMA expression in fibroblasts through Notch1 signaling ¹²⁸. TNF has also demonstrated pro-fibrotic roles in several pathologies, through the induction of collagen synthesis, proliferation and

354

355

356 357

358

359

360

361

362

363

364

365

366

367

368 369

370

371

372 373

374

375

376

377

378 379

380

381

382 383

384

385 386

387

388

389

390

391

392

393 394

395

activation of myofibroblasts 129,130 . IL-1 β further drives fibrotic outcomes through indirect promotion of IL-6, TGF- β and PDGF ¹³¹, although the mechanism is less obvious and warrants further study ¹³². FGF-2, TGFβ, TNFα, PDGF as secreted by macrophages and FBGCs have been associated with myofibroblastic activity and wound/implant fibrosis and fibrotic disease pathology ^{11,37,114,133}. Heightened local VEGF levels have been associated with both increased ⁹ and decreased ^{134,135} fibrosis. Local ischemia can induce VEGF secretion, which can both support increasing capsular formation, or stabilize healthy healing interstitium; VEGF control can therefore potentiate both pro-fibrotic and proregenerative FBRs based on other physical, chemical, and temporal cues ¹³⁶.

The interaction between macrophages and fibroblasts extends beyond the promotion of fibrosis through myofibroblast induction. Macrophages act as potent sources of matrix metalloproteinases (MMPs), which can impact fibrosis directly via ECM degradation, or indirectly through cellular signaling and regulation of inflammation 137. The roles of MMPs in fibrotic control are extensive and highly context dependent. For example, MMP-9 expression or activity has variably shown pro-fibrotic, neutral, or anti-fibrotic roles among different models of lung fibrosis ¹³⁷. The roles of MMPs in FBR-specific fibrosis are not entirely understood. Current understandings are summarized in Table 2. Additionally, macrophages can also limit fibrosis through IL-10 signaling, which reduces collagen production in activated myofibroblasts 5,85,91,138-140. Arg1 metabolic flux in macrophages has also been associated with reduced fibrosis. Though the mechanism remains unclear, a possible explanation could involve 'substrate stealing', wherein the highly metabolically active oxidative macrophages reduce available arginine for collagen production by fibroblasts 45,84.

3. Advances in profiling and mitigating the foreign body response

Growing clinical evidence continues to establish causation and is demonstrating the significant burden of pathology attributable to the foreign body response. With increased attention, rapid advancements in both clinical and translational science are outlining new ways to interrogate and mitigate the FBR. Below, we outline exciting new approaches to profiling clinical disease, new in vitro and in vivo models of the FBR, and therapeutic strategies in development to avoid or treat FBR incidence.

Investigating the foreign body response: models and techniques 3.1.

As a complex phenomenon involving many lineages of cells and a highly context-dependent timeline, most mechanistic investigations of the FBR have benefitted from the use of animal models, informed by available clinical explants. These animal models and associated analyses have recently been expertly summarized in the context of hernia meshes, a well-studied and clinically significant example of the FBR 141, with efforts to better model metabolic and biomechanical considerations often prompting the use of larger animal models 142. With growing concern about the clinical adaptation of hernia mesh to pelvic organ prolapse, similar animal models of vaginal mesh application have been developed ^{143,144}, as has a model of neural implant FBR ⁷², and models of silicone-implant associated capsular contracture ^{29,145}. Concerning the development of biocompatible materials to ameliorate the FBR, studies are often complicated by differences between and even within standardized animal lines by individual variability and by batch effects of implantation runs, both in terms of animal and implant batches ^{57,146}. The use of well-designed and statistically-informed experimental and surgical procedures can mitigate many of these complications, such as in the combinatorial screening of multiple materials in mice, which was successfully translated to primate usage 147. From both model system and patient explants, single-cell techniques for functional profiling continue to be developed and standardized for replication and translation 148; findings from multi-omics studies may be transferrable across species, experiments, and lines with the appropriate standardization and controls ¹⁴⁹.

From both in vivo models and with clinical explants, improved characterization techniques are helping to elucidate spatial relationships in the FBR. Cell profiling in situ with histology can allow for more precise profiling of cell phenotype and interactions in the local region ^{43,55}, while spatial transcriptomics of granulomas allow for cell

interaction profiling ¹⁵⁰. Intravital microscopy, by allowing repeated individual measures over time, allows for highly mechanistic studies to also inform factors of individualized response ⁹. Individual genetics, medical history, and these intersecting and non-linear contributors to an individual's immune response are also more understood than ever, and inquiry and design with these concepts in mind will help to account for and harness individual variability in immunity ¹⁵¹.

While in vivo models of the FBR provide valuable translational direction and holistic biometrics, they often fail to provide detailed mechanistic insight or quantitative metrics for optimization of therapeutic design. Immunology has benefitted significantly from recent advances in reproducible in vitro experimentation, and investigation of the FBR specifically is likely to benefit similarly from the level of mechanistic resolution that in vitro approaches provide. For example, new models of FBGC fusion in vitro 42,152 will allow for understanding of the factors leading to FBGC formation, as well as elucidate their functionality and amenability to productive control to then be trialled in vivo. Approaches to screening materials are well-established in vitro, although immunoregulatory applications are still very novel; macrophage M1/M2 differentiation was successfully profiled on combinatorial copolymer libraries in a recent study ¹⁵³, an approach that will prove instructive for further efforts. Similarly, statistically informed approaches reach a level of throughput that in vivo approaches cannot practically accommodate. Studies have revealed multifunctionality of individual cell phenotypes, and complex bidirectional relationships between macrophages and other stromal cells. Use of high-factor multivariate optimization encompassing genes, soluble excreted protein expression (e.g. VEGF), and microscopy-derived morphometrics (e.g. vascular tube formation and cell diameter) allowed for multiparametric optimization of macrophage-directed interstitial cell function in vitro 154. These techniques can be used not only to model the peri-implant environment for material and therapeutic development, but also to derive quantitative multifactorial cause and effect mechanisms of immune function in situ.

As immunometabolism is a rapidly-growing field, so too are approaches by which to profile it. Traditional extracellular flux approaches such as those offered by Agilent Seahorse systems have successfully been used to profile specific pathway control in immune populations ^{155,156}. However, flow cytometry-based approaches to profile single-cell metabolism not only offer greater resolution of rare populations and limited samples *in vitro* or *in vivo*, but allow for correlation to cell phenotype by coupling to simultaneous traditional flow cytometric analyses, such as in the SCENITH method of profiling central carbon metabolism ¹⁵⁷ and the QUAS-R method of profiling glutamine uptake ¹⁵⁸. Finally, metabolomic profiling allows for targeted pathway flux analysis ^{159,160}, which can be adapted for use in FBR characterization.

3.2. Material properties influencing the foreign body response

A degree of fibrosis is an expected outcome of wound healing, and thus will be present following implantation with any biomaterial. In fact, a physiological level of fibrosis is desired for mechanical stabilization and tissue integration of most implants ¹⁶¹. Nevertheless, aberrant FBR outcomes are associated with costly implant revisions, highlighting the importance of understanding the dynamics of the biomaterial-host interactions. The extent to which material properties can alter fibrous encapsulation during the FBR has been outlined in previous reviews^{11,36,100,162}. The mechanical properties of implanted materials are considered paramount to stable integration with host tissues. Mismatch between the stiffness of host tissue and an implant result in mechanical disruptions and worsen fibrosis^{12,163}. Additionally, implant topography and scale can significantly alter the FBR. Jagged edges and macroscopic texturing that promote continuous tissue disruptions are associated with severe FBR outcomes ¹¹. Conversely, micro- and nano-texturing can impact adhesion and orientation of proteins, the patterning of cells, and ultimately mitigate adverse FBR outcomes ^{164,165}. A material's degradative profile is also believed to impact the FBR. Where material degradation is possible, implant fragmentation is conducive to both phagocytosis and discontinuous capsule formation, contributing to lower rates of capsular contracture and implant failure.

Material properties which influence the rate of protein adsorption at the implant interface are thought to be equally important in determining the outcome of the FBR. Some of the commonly identified characteristics that alter adsorption rates (and thus potentially affect the FBR) include surface roughness, surface charge and hydrophobia/hydrophilia 5. Hydrophobicity/wettability will partially determine the degree of protein adsorption to its surface; hydrophilic surfaces resist protein adsorption relative to hydrophobic surfaces and are accordingly associated with less severe fibrotic reactions ^{166,167}. The surface charge of the material also in part determines the degree of protein adsorption to an implant, where increased charge increases protein adsorption 168. Fibroblast traction based on both material stiffness and protein adsorption can influence macrophage migration and thus potentially chemotactic gradient formation, potentially creating positive feedback loops ¹⁶⁹; implants or factors that influence ECM deposition could therefore have outsized effects. Hence, implants of different materials might result in different levels of inflammation, and consequently the fibrosis following implantation. Understanding the metabolic differentiation in macrophages for different materials could elucidate some of the metabolic processes involved in a successful FBR outcome. However, the generation of particulates and degradation products from the material, or metabolites released from cells responding to the material, may result in local toxicity leading to unintended effects. Careful and systematic characterization of material disposition and mechanism of action of therapy will be required to ensure safety and efficacy of novel therapeutic materials.

Additionally, a better understanding of effector material properties will be critical in identifying potential targets for novel therapies, in addition to improving our understanding of the interplay between metabolism, signalling and effector function. Among the most commonly used medical implant materials are: poly(lactic-co-glycolic) acid (PLGA), polypropylene (PP), polyethylene (PE), polycaprolactone (PCL), polyethylene glycol diacrylate (PEGDA) and polydimethylsiloxane (PDMS). PP is preferentially used for permanent support-lending applications such as structural meshes and sutures ¹⁷⁰. PE implants are used in facial reconstruction as well as in joint replacement surgeries ¹⁷¹. PCL implants are often used in cranioplasty ¹⁷², and PDMS is commonly used for breast implants ⁴. PLGA has a wide range of popular applications including tissue engineering scaffolding and micro- and nanoparticle delivery systems, is bio-degradable, and as such is considered to be highly biocompatible ¹⁷³. With a variety of materials available, each likely with inherent physicochemical properties, there is much to be learned about macrophages in the response to different IMD materials.

3.3. Biomaterial chemistry-based strategies to mitigate FBR pathology: physical, chemical, and immune-signaling

Significant effort has been expended in profiling various physicochemical approaches to minimizing immunoreactivity and fibrosis to implanted materials. Alterations to physical properties outlined above, including wettability, stiffness, charge, (nano)topography and porosity have demonstrated clear trends in mitigating the FBR through altered rates of protein adsorption (**Figure 2**) ¹⁶². Additionally, patterning of the surface that mimics features of the surrounding tissue has been shown to lead to a reduction of fibrosis through biomimicry, though this is not always possible or beneficial ¹⁷⁴. Changes to surface topography, such as micro-texturing, have demonstrated success in reducing implant-induced fibrosis *in vivo*, with relevant translation into the clinical setting for breast reconstructive surgeries. However, alarming links between micro-textured implants and the development of breast-implant-associated anaplastic large cell lymphoma (BIA-ALCL) have resulted in a market recall ^{175,176}. Similarly, polyurethane foam coatings for silicone breast implants have been associated with reductions in capsular contracture rates in cases where the coatings remain intact. Here, the porosity and texturing of the foam is thought to disrupt spatially continuous capsule formation and effectively dissipates mechanical tension ¹⁷⁷, albeit with risks of pathology such as ALCL as discussed above. However, concerns with regards to material degradation and toxicity have resulted in caution toward such implementations; the benefit of similar form designs with other materials remain undercapitalized.

485

486 487

488 489

490

491

492

493

494

495

496

497

498

499

500 501

502

503

504

505

506 507

508

509 510

511

512

513 514

515

516

517518

519

520

521

522

523

524

525

526527

528 529

530

Implant surface coatings have demonstrated the highest degree of success in reducing implant fibrosis. Zwitterionic materials/coatings and polyethylene glycol (PEG) surface conjugation have exhibited antifouling properties through decreasing adsorption of host proteins (i.e. ECM and DAMPs) to the implant surface ^{35,114,178}. This leads to a reduction in immune cell recruitment, macrophage recognition and activation, and proinflammatory cytokines ^{147,179,180}. Nonsynthetic protein (e.g., gelatin and fibronectin) ^{39,181,182}, polysaccharide (hyaluronic acid, alginate, pectin, and heparin) ^{147,182–187}, and cytokine ¹⁸⁸ polymer coatings have been used to reduce cellular activation by improving biocompatibility between the implant surface and tissue microenvironment. Similarly, use of a xeno/allo-derived adipose ECM extract showed improved biocompatibility and CD4 T-cell/M2 macrophage activation relative to gross fat when implanted in soft tissue ¹⁸⁹. While immunoevasion or biomimicry methods are useful in decreasing the acute FBR, they do not fully prevent host protein, ECM, and DAMP adsorption to the material, and downstream chronic immune cell activation. Therefore, strategies to target the FBR over long-term implantation are required; immunomodulation has become the major strategy to improve implant material outcomes in chronic settings ¹⁹⁰.

Research into immunomodulation to combat the FBR has been focused primarily on anti-fibrotic drug release/elution from material surfaces. In contrast to immunoevading materials, which either evade or integrate the inflammatory response, immunomodulating materials/systems actively supress the inflammatory response through drug delivery. The simplest of these systems employ anti-fibrotic drug harbouring coatings which passively elute drug from the material surface 191,192. Most of these models focus on the release of dexamethasone as a drug of choice due to its potent anti-inflammatory properties ¹⁹³⁻¹⁹⁵ and utility in the case of long-lasting implants ¹⁹⁶. Dexamethasone serves as an excellent model of coating chemistries and hydrophobic drug release ^{13,146,193–196}, and is highly effective at minimizing FBR. However, there are two key weaknesses in the translation of passive dexamethasone-eluting materials: 1) non-discriminating local immunosuppression is contraindicated for real-world surgeries due to the inevitability of occasional surgical site infections ¹⁹⁷, 2) dexamethasone impairs pro-regenerative responses 72. Apart from dexamethasone, many other anti-fibrotic drugs such as methotrexate 198, pirfenidone 199, triamcinolone ^{200–202}, and tranilast ²⁰³ have shown efficacy in reducing implant induced fibrosis. Additionally, some non-traditional anti-fibrotic molecules such as kynurenic acid 204, colony-stimulating factor 1-inhibitor GW2580 205, NLRP3 inhibitor MCC950 72, rapamycin 206 and sirolimus 207, cytokines (e.g., IL-4 eluting materials) 208, and immunotherapies (e.g., parasite antigens) 209 have all been shown to reduce implant induced fibrosis over various models.

Finally, justified concern of pathological fibrosis and surgical site infection has spurred the continued development of biologically derived implantable materials. These are most visible in applications for structural support, such as in surgical sutures and biological meshes for use in various hernia repairs (e.g., primary or incisional abdominal hernias, hiatal hernias, and inguinal hernias), as more specialized functional implants do not have biological options. Suture choice is heavily dependent on the tissue in question, as well as surgeon comfort or preference. Silk and gut sutures remain in active use for specialized indications; with the former being effectively permanent. Silk sutures offer advantages in handling, but are rarely strictly biologic in modern times as they often carry synthetic coatings. Overall, silk sutures offer little advantage in terms of both fibrosis (they remain highly immunogenic) and infection risk (as their braided design increases pathogen growth capacity) ²¹⁰⁻²¹². In terms of meshes for surgical plane repair, absorbable meshes, both biological and synthetic, have existed for decades. Biological meshes vary in terms of animal and tissue source, chemical crosslinking, and additives, and are designed with the intention to facilitate host tissue ingrowth before resorption renders them structurally noncontributory. These meshes are also often used in contaminated procedures in an effort to reduce the risk of surgical site infection, however infection rates, recurrence, and chronic pain suggest that biological meshes have no benefit over synthetics ^{213–215}. Absorbable synthetic meshes, although contentious in terms of their risk of hernia reoccurrrence ²¹⁶, are generally growing in acceptance 142,217-219, although judicious implant selection is still required when balancing patient demographics, anatomical considerations, and infection risks. In light of the high cost and uncertain benefit of biological materials in such a niche, it is likely that newer generations of chemically-defined synthetic products, both permanent and absorbable, will continue to grow in utility.

532533

534 535

536

537

538

539 540

541

542 543

544 545

546

547

548 549

550

551

552

553

554 555

556

557

558

559 560

561

562

563 564

565 566

567 568

569

570571

572

573

574

3.4 Immunometabolism as a promising therapeutic target to control the FBR

Recent advancements in the field of immunometabolism highlight the potential of multiple small molecule metabolites to regulate the FBR and associated material-induced fibrosis ²²⁰. Small molecules such as TCA metabolites have all shown promise in regulating the FBR ^{159,221–225}. In particular, the metabolite itaconate (IA) has emerged as a potent regulator of macrophage phenotype ^{226–228}. Itaconate has diverse direct and indirect immunomodulatory roles, including inhibition of both glycolytic and TCA pathways, multipronged inhibition of the NLRP3 inflammasome, and inhibition of myofibroblast activity, together allowing IA and its isomers to participate in highly specific contextual immunoregulation ^{226,227,229–231}. IA can target classically activated macrophages due to its potent anti-inflammatory effects, and can equally target alternatively activated macrophages by blocking monocyte differentiation into M(IL-4) ^{222,232–234}. In addition to TCA metabolites, glycolytic metabolites and analogues also demonstrate promising immunoregulatory activity. For example, incorporation of the glycolytic inhibitors 2-deoxyglucose and aminooxyacetic acid in subcutaneous polylactide (PLA) implants induced an anti-inflammatory phenotype ²³⁵. PLGA has equally shown the ability to intrinsically exert metabolic control over local cells ²³⁶. As mentioned above, when working with such chiral metabolites, validation of the stereochemistry of the formulation in question is crucial, and requires further standardization and control in studies ²³⁷.

Despite its promise in precise and context-specific control of the immune response, immunometabolism presents several inherent challenges before it can be effectively leveraged in clinical practice. As demonstrated above, metabolites require relatively high concentrations before reaching therapeutic concentrations relative to many other bioactive molecules. This therefore poses a difficult engineering challenge to deliver doses safely to the target region. Chemical stability of bioactive components is also a consideration for all designs. Finally, these therapeutics need to be chemically and logistically compatible with the IMD in question. A potential solution to all of these individual challenges lies in the design of smart biomaterials. For example, metabolites such as IA require relatively high dose delivery to effectively modulate the immune system (5-10 mmol L⁻¹) ^{238,239}. Passive drug-eluting surfaces fail to sustain effective high concentration drug delivery over long-term inflammation ^{240,241}. As such, with limited loading capacity, passive-drug eluting systems could be tailored to either deliver short-term high dose, or long-term low dose drug release. In the case of small molecule delivery, such as IA, a different approach to drug delivery needs to be taken to allow for high dose release in the long-term. IA, as well as other TCA metabolites, can be synthesized into the backbone of polyester polymetric biomaterials ²⁴⁰. As the material is degraded in the host environment, the eluted metabolites regulate the fibrotic microenvironment. This method of drug delivery has two advantages over passive diffusion. Firstly, it greatly increases the loading capacity of the material ^{241,242}. Secondly, polymeric degradation can be tunable for temporal specific increased drug delivery ^{242–244}. Polymeric degradation kinetics rely on a variety of intrinsic polymer characteristics. Co-polymer ratio, molecular weights, polydispersity, material viscosity, transition temperatures, polymer endcaps, and hierarchical structuring (e.g., branching) are all useful tools in modulating degradation profiles and drug delivery ²⁴⁵. This may provide a novel biomimetic avenue to reduce FBR-associated complications in future work.

4. Conclusions and future perspectives

Ultimately, the current understandings of FBR-associated fibrosis summarized in this paper indicate complex cellular heterogeneity and dynamic behaviours. The macrophage-fibroblast signalling axis is key to the development of capsular contracture and implant failures, but significant gaps remain in our understanding of the underlying mechanism and therefore potential targets. Critically, FBGC formation is a notable hallmark progression of the FBR but these cells share features of both M1 and M2 macrophages and defy canonical classification. Here, immunometabolism offers a promising new approach to cellular phenotyping in the implant microenvironment. Where the conventional immunological paradigm fails to capture the totality of cellular dynamics in the FBR,

This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.

Open Access Article. Published on 27 juli 2024. Downloaded on 04-08-2024 11:14:49.

evidence supporting links between metabolic behavior and pathological fibrotic signalling is abundant, underscoring the need for a comprehensive immunophenotyping of the tissue-implant microenvironment. Availability of effective treatment options to mitigate pathological fibrosis in the FBR is equally limited. The functionality of minor levels of fibrosis in improving tissue-implant integration, as well as the putative importance of early inflammation in promoting angiogenesis and tissue sterilization should caution the usage of broad-spectrum anti-inflammatory drugs such as dexamethasone. Additionally, currently available treatments lack tuneable release systems with sufficient reservoirs needed to promote extended release of anti-inflammatory drugs during the chronic stages of inflammation associated with pathological fibrosis in the FBR. The development of novel treatments is required to allow the temporal control of pharmacological interventions required to treat pathological inflammation and fibrosis in the FBR. Critically, FBR study is challenged by the lack of *in vitro* models available to recapitulate the complexity of the tissue-implant microenvironment, to overcome both the logistical and inherent immunological challenges in translating animal studies. Efforts are required to improve and develop better models of the FBR, with improved clinical translatability. Finally, major outstanding questions remain as to the clinical risk factors associated with undesirable FBR outcomes. Robust prospective analyses describing early patient phenotypes correlated to downstream clinical outcomes would help identify risk factors associated with FBR complications.

Ultimately, this review has served to summarize current understandings of the FBR to implanted biomaterials, as well as identify critical gaps requiring future investigation and development. This review has benefitted from significant recent attention to the mechanisms underlying immunometabolic regulation, as well as efforts in translating this knowledge to practical effect.

5. Data Availability Statement

No primary research results, software or code have been included and no new data were generated or analysed as part of this review.

6. Acknowledgements

This research is supported by the Dalhousie Medical Research Foundation Faculty of Dentistry Early Career Research Award, Natural Sciences and Engineering Research Council of Canada (NSERC) Discovery Grant (RGPIN-2022-03666), and New Frontiers in Research Fund – Exploration Fund (NFRFE-2022-00313). NC was supported by an award from the Webster Family Fund for Research in Immunology and Genetics. ZF was supported by an NSERC Canada Graduate Scholarship – Masters, Nova Scotia Graduate Scholarship, and Killam Predoctoral Scholarship (Masters).

7. Author contributions

NIC conceived the manuscript. NIC, CR, ZF, KM wrote the manuscript. NIC, CR, ZF, KM and LDH edited the manuscript and approved the final version.

8. Conflict of interest

The authors declare no conflict of interest.

9. Display items

611

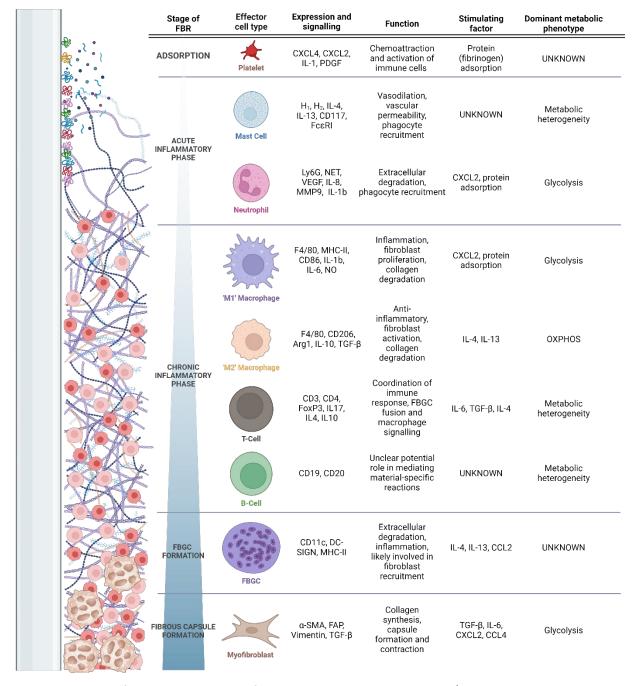


Figure 1: Timeline of the FBR, recruitment of associated cells, and their secretory/metabolic phenotypes.

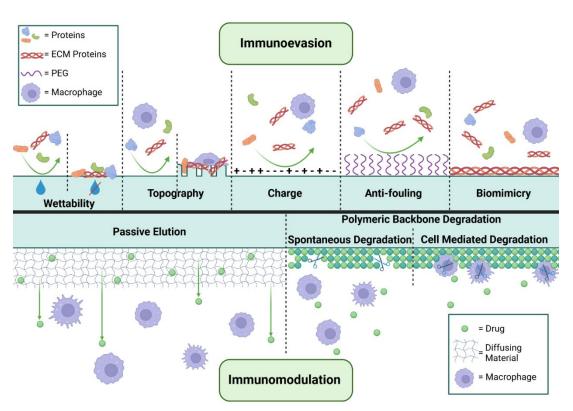


Figure 2: Biomaterial design strategies to mitigate the immune-driven foreign body response.

Table 1: Cytokines associated with the FBR. 618

Cytokine	Cellular Origin	Target Cell	Function	Source(s)
			Promotes activation of	
TOT 0		F11 11	fibroblasts. Promotes	5,89,90
TGF-β	Macrophages, fibroblasts	Fibroblasts, Macrophages	'anti-inflammatory' profile	5,89,90
			in macrophages.	
			Promotes differentiation	
	'M1-like' macrophages,		and proliferation of	
TNFα	neutrophils	Macrophages	myofibroblasts. Promotes	129,130
	neatropinis		inflammation.	
			Macrophage and	
			fibroblast recruitment.	
PDGF	Macrophages, platelets,	Macrophages, Fibroblasts	Promotes myofibroblast	7,11,127,136
. 56.	fibroblasts	Wider opringes, Fish obligats	differentiation and	
			angiogenesis.	
			Promotes formation of	
	'M1-like' macrophages,		neo-vasculature.	
VEGF	FBGCs	Endothelial cells	Associated with elevated	9,11,136
	1 BGCS		fibrosis.	
			Induces alterations to	
			MMP secretion profiles.	
IL-1β	'M1-like' macrophages,	Macrophages	Promotes inflammation	131,132
ir-1b	neutrophils		and expression of pro-	.,.
			fibrotic mediators.	
		Macrophages	Promotes alternative 'anti-	
IL-4	Mast cells, T-cells		inflammatory' activation	7,92,93
			of macrophages. Believed	
			to play a role in cell fusion. Promotes activation of	
			fibroblasts and stimulates	
IL-6	Macrophages	Macrophages, Fibroblasts	paracrine TGF-β signalling.	125,126,249
	. 5		Primes macrophages for	
			anti-inflammatory	
			signaling.	
			Reduces collagen and α-	
		Macrophages, Myofibroblasts	SMA expression in	
IL-10	'M2-like' macrophages		activated fibroblasts.	5,85,91,138-140
			Promotes anti-	
			inflammatory macrophage	
			phenotype.	
		Macrophages	Promotes alternative 'anti-	
IL-13	Mast Cells, T-cells		inflammatory' activation	7,92,93
12 13	Wast cens, 1 cens	Macrophages	of macrophages. Believed	
			to play a role in cell fusion.	
			Undifferentiated role in	
			promoting chronic	
IL-17	7 Th17 cells	Neutrophils, Macrophages, Monocytes	fibrosis. Associated with	59
1L-1/			increased monocyte,	
			macrophage, and	
			neutrophil presence.	

ММР	Classification	Macrophage phenotype	Co-associated genes/products	Temporal trend in expression	Niche/implant location	Species	Material	Technique	Reference
2	Gelatinase	(Gross analysis of explanted collagen disk)	IL-1α, TNFα, TGFβ	Progressive increase	Subcutaneous	Mouse	Bovine collagen	PCR gel	2
		CD163+/CD206+	Col-I	0.6-6 years post- implantation	Abdominal wall	Human	Polypropylene	Immunofluorescence microscopy	3
8	Collagenase	(Gross analysis of explanted collagen disk)	IL-1β, IL-10, CXCL1, CXCL2	Acute; decline after 1 week	Subcutaneous	Mouse	Bovine collagen	PCR gel	2
		(Gross analysis of explanted collagen disk)	IL-1α, TNFα, TGFβ	Appearance after 2 weeks	Subcutaneous	Mouse	Bovine collagen	PCR gel	2
	Gelatinase	Proliferative macrophage ("MD2")	Proliferation- associated products	[Not characterized]	Subcutaneous	Rat	Silk	scRNAseq	4
		Adherent macrophage and FBGCs*	Adhesion- associated products	Significant increase in 3 days	In vitro	Human	PET, and modified PET	Antibody array and quantitative ELISA	246
9		(Gross analysis of explanted capsule breast implant tissue)	Rac2	Increasing with increased Baker score	Breast	Human	Silicone	Bulk RNAseq	247
		FBGCs	Macrophage fusion, ECM degradation	[Not characterized]	Subcutaneous	Mouse	Mixed cellulose ester disks and polyvinyl alcohol sponges	Immunohistochemistry antibody array	248
12	Stromelysin	Giant cell ("C7")	ECM degradation, macrophage fusion, complement receptors, glycolysis	Progressive increase; resolution between 2-4 weeks in resorbable silk but not sponge	Peritoneal	Mouse	Silk and sponge (putatively cellulose)	scRNAseq	5
		Giant cell -like ("MD1")	ECM degradation	Intermediate	Subcutaneous	Rat	Silk	scRNAseq and histology	4
		Giant cell-like ("MD3")	Macrophage fusion, oxidative function	Progressive increase to 2 weeks	Subcutaneous	Rat	Silk	scRNAseq and histology	4

Page 20 of 32

		Gros analysis of explanted capsule breast implant tissue)	Il-8, Tnsf11	[Not characterized]	Breast	Human	Silicone	qPCR	30
13	Collagenase	(Gross analysis of explanted collagen disk)	IL-1α, TNFα, TGFβ	Increasing after 2-3 weeks	Subcutaneous	Mouse	Bovine collagen	PCR gel	2
14 Membrane	Membrane	Epithelioid ("C6")	Pro- inflammatory (IL1b), ECM, chemokines	Progressive increase; resolution between 2-4 weeks in resorbable silk but not sponge	Peritoneal	Mouse	Silk and sponge (putatively cellulose)	scRNAseq	5
	type	(Gross analysis of explanted collagen disk)	IL-1α, TNFα, TGFβ	Increasing 2-3 weeks post implant	Subcutaneous	Mouse	Bovine collagen	PCR gel	2
		(Gross analysis of explanted CC breast implant tissue)	Rac2	Increasing with increased Baker	Breast	Human	Silicone	Bulk RNAseq	247
19	Not classified	Epithelioid ("C6")	Pro- inflammatory (IL1b), ECM, chemokines	Progressive increase; resolution between 2-4 weeks in resorbable silk but not sponge	Peritoneal	Mouse	Silk and sponge (putatively cellulose)	scRNAseq	5
MT3 (MMP 16)	Membrane type	Giant cell-like ("MD3")	Macrophage fusion, oxidative function	Progressive increase to 2 weeks	Subcutaneous	Rat	Silk	scRNAseq and histology	4
(Minimal)		M2-like (C5)	IL-10, chemokines	Acute, resolving in both resorbable suture and nonresorbable sponge	Peritoneal	Mouse	Silk and sponge (putatively cellulose)	scRNAseq	5

This article is licensed under a Creative Commons Attribution 3.0 Unported Licence. Open Access Article. Published on 27 juli 2024. Downloaded on 04-08-2024 11:14:49.

References 10. 622

- 623 K. A. Schlosser, S. M. Renshaw, R. M. Tamer, S. A. Strassels and B. K. Poulose, Hernia, 2022, 27, 415-421.
- 624 Q. Ma, W. Jing, X. Liu, J. Liu, M. Liu and J. Chen, Int. J. Surg. 2
- 625 M. P. Simons, M. Smietanski, H. J. Bonjer, R. Bittner, M. Miserez, T. J. Aufenacker, R. J. Fitzgibbons, P. K. Chowbey, H. M. Tran, R. Sani, F. Berrevoet, J. Bingener, T. Bisgaard, K. Bury, G. Campanelli, D. C. Chen, J. 626
- 627 Conze, D. Cuccurullo, A. C. de Beaux, H. H. Eker, R. H. Fortelny, J. F. Gillion, B. J. van den Heuvel, W. W.
- 628 Hope, L. N. Jorgensen, U. Klinge, F. Köckerling, J. F. Kukleta, I. Konate, A. L. Liem, D. Lomanto, M. J. A. Loos,
- 629 M. Lopez-Cano, M. C. Misra, A. Montgomery, S. Morales-Conde, F. E. Muysoms, H. Niebuhr, P. Nordin, M.
- Pawlak, G. H. van Ramshorst, W. M. J. Reinpold, D. L. Sanders, N. Schouten, S. Smedberg, R. K. J. 630
- Simmermacher, S. Tumtavitikul, N. van Veenendaal, D. Weyhe, A. R. Wijsmuller and T. H. Group, Hernia, 631
- 632 2018, **22**, 1-165.
- H. Headon, A. Kasem and K. Mokbel, Arch. Plast. Surg., 2015, 42, 532-543. 633 4
- 634 R. Klopfleisch and F. Jung, J. Biomed. Mater. Res. - Part A, 2017, 105, 927-940.
- 635 O. Veiseh and A. J. Vegas, Adv. Drug Deliv. Rev., 2019, 144, 148-161. 6
- 636 7 J. M. Anderson, A. Rodriguez and D. T. Chang, Semin. Immunol., 2008, 20, 86–100.
- 637 8 J. Elisseeff, S. F. Badylak and J. D. Boeke, N. Engl. J. Med., 2021, 385, 2451–2462.
- 638 9 E. Dondossola, B. M. Holzapfel, S. Alexander, S. Filippini, D. W. Hutmacher and P. Friedl, Nat. Biomed. Eng., 639 2017, **1**, 0007.
- 640 10
- S. Gentile, F. Strollo, T. Della Corte, G. Marino and G. Guarino, Diabetes Res. Clin. Pract., 2018, 138, 284-641
- 642 A. Carnicer-Lombarte, S. T. Chen, G. G. Malliaras and D. G. Barone, Front. Bioeng. Biotechnol., 2021, 9, 1– 11 643
- 644 12 M. Gori, G. Vadalà, S. M. Giannitelli, V. Denaro and G. Di Pino, Front. Bioeng. Biotechnol.,
- 645 DOI:10.3389/fbioe.2021.659033.
- 646 13 N. De la Oliva, X. Navarro and J. del Valle, *Anat. Rec.*, 2018, **301**, 1722–1733.
- 647 14 J. W. C. Tervaert, Y. Shoenfeld, C. Cruciani, C. Scarpa and F. Bassetto, Autoimmun. Rev., 2023, 2, 103448.
- 648 15 J. E. Ireton, J. G. Unger and R. J. Rohrich, Plast. Reconstr. Surg. Glob. Open, 2013, 1, 1-10.
- C. L. Baum and C. J. Arpey, *Dermatologic Surg.*, 2005, **31**, 674–686. 649 16
- 650 17 R. B. Wilson and Y. Farooque, J. Gastrointest. Surg., 2022, 26, 950–964.
- 651 18 A. L. Vorst, World J. Gastrointest. Surg., 2015, 7, 293.
- 652 19 M. J. Tolino, D. E. Tripoloni, R. Ratto and M. I. García, Hernia, 2009, 13, 631-637.
- 653 20 D. J. Tubre, A. D. Schroeder, J. Estes, J. Eisenga and R. J. Fitzgibbons, Hernia, 2018, 22, 1003–1013.
- 654 21 D. Wouters, G. Cavallaro, K. K. Jensen, B. East, B. Jíšová, L. N. Jorgensen, M. López-Cano, V. Rodrigues-
- 655 Gonçalves, C. Stabilini and F. Berrevoet, Front. Surg., 2022, 9, 847279.
- 22 A. Ríos, J. M. Rodríguez, V. Munitiz, P. Alcaraz, D. Pérez Flores and P. Parrilla, Hernia, 2001, 5, 148–52. 656
- 23 F. Ali, G. Sandblom, A. Wikner and G. Wallin, Hernia, 2022, 26, 635–646. 657
- M. Cevasco and K. M. F. Itani, Surg. Infect. (Larchmt)., 2012, 13, 209-215. 658 24
- 659 25 K. Baylón, P. Rodríguez-Camarillo, A. Elías-Zúñiga, J. A. Díaz-Elizondo, R. Gilkerson and K. Lozano,
- Membranes (Basel)., 2017, 7, 1–23. 660

- K. Lockhart, D. Dunn, S. Teo, J. Y. Ng, M. Dhillon, E. Teo and M. L. van Driel, *Cochrane Database Syst. Rev.*, 2018, **2018**, CD011517.
- S. M. Smith, A. A. Khoja, J. H. W. Jacobsen, J. G. Kovoor, D. R. Tivey, W. J. Babidge, H. S. Chandraratna, D. R. Fletcher, C. Hensman, A. Karatassas, K. W. Loi, K. M. F. McKertich, J. M. A. Yin and G. J. Maddern, *ANZ J. Surg.*, 2022, **92**, 2492–2499.
- 666 28 M. T. Nguyen, R. L. Berger, S. C. Hicks, J. A. Davila, L. T. Li, L. S. Kao and M. K. Liang, *JAMA Surg.*, 2014, **149**, 667 415–421.
- 668 29 F. T. Foroushani, K. Dzobo, N. P. Khumalo, V. Z. Mora, R. de Mezerville and A. Bayat, *Biomater. Res.*, 2022, **26**, 1–27.
- I. Brigaud, C. Garabédian, N. Bricout, L. Pieuchot, A. Ponche, R. Deltombe, R. Delille, M. Atlan, M. Bigerelle
 and K. Anselme, *Plast. Reconstr. Surg.*, 2020, **145**, 542e-551e.
- 672 31 A. Seifalian, Z. Basma, A. Digesu and V. Khullar, Biomedicines, 2023, 11, 741.
- Independent Medicines and Medical Devices Safety Review, First Do No Harm: The report of the Independent Medicines and Medical Devices Safety Review, 2020.
- A. Padoa, A. Braga, T. Fligelman, S. Athanasiou, C. Phillips, S. Salvatore and M. Serati, *Urogynecology*, 2023, **29**, 703–716.
- 677 34 B. Welk, K. V. Carlson, R. J. Baverstock, S. S. Steele, G. G. Bailly and D. R. Hickling, *Can. Urol. Assoc. J.*, 2017, 678 **11**, 105.
- 679 35 M. D. Swartzlander, C. A. Barnes, A. K. Blakney, J. L. Kaar, T. R. Kyriakides and S. J. Bryant, *Biomaterials*, 680 2015, **41**, 26–36.
- 681 36 E. Mariani, G. Lisignoli, R. M. Borzì and L. Pulsatelli, Int. J. Mol. Sci., , DOI:10.3390/ijms20030636.
- 682 37 N. Noskovicova, B. Hinz and P. Pakshir, Cells, , DOI:10.3390/cells10071794.
- A. Balabiyev, N. P. Podolnikova, J. A. Kilbourne, D. P. Baluch, D. Lowry, A. Zare, R. Ros, M. J. Flick and T. P. Ugarova, *Biomaterials*, 2021, **277**, 121087.
- B. G. Keselowsky, A. W. Bridges, K. L. Burns, C. C. Tate, J. E. Babensee, M. C. LaPlaca and A. J. García,
 Biomaterials, 2007, 28, 3626–3631.
- 687 40 J. S. Roh and D. H. Sohn, *Immune Netw.*, 2018, **18**, e27.
- Q. Wei, T. Becherer, S. Angioletti-Uberti, J. Dzubiella, C. Wischke, A. T. Neffe, A. Lendlein, M. Ballauff and R. Haag, *Angew. Chemie Int. Ed.*, 2014, **53**, 8004–8031.
- 690 42 A. Kaushal, Y. Zhang, L. L. Ballantyne and L. E. Fitzpatrick, Front. Bioeng. Biotechnol., 2022, 10, 1–19.
- 691 43 U. Klinge, A. Dievernich and J. Stegmaier, *Front. Med.*, 2022, **9**, 1–15.
- J. I. Crossley, S. Ostashevskaya-Gohstand, S. Comazzetto, J. S. Hook, L. Guo, N. Vishlaghi, C. Juan, L. Xu, A. R.
 Horswill, G. Hoxhaj, J. G. Moreland, R. J. Tower and B. Levi, *JCI Insight*, DOI:10.1172/jci.insight.169208.
- 694 45 L. Moretti, J. Stalfort, T. H. Barker and D. Abebayehu, *J. Biol. Chem.*, 2022, **298**, 101530.
- 695 46 D. M. Simpson and R. Ross, *J. Clin. Invest.*, 1972, **51**, 2009–2023.
- 696 47 P. T. Thevenot, D. W. Baker, H. Weng, M. W. Sun and L. Tang, Biomaterials, 2011, 32, 8394–8403.
- 697 48 L. Tang, T. A. Jennings and J. W. Eaton, *Proc. Natl. Acad. Sci. U. S. A.*, 1998, **95**, 8841–8846.
- 698 49 L. Tang and J. W. Eaton, *Mol. Med.*, 1999, **5**, 351–358.
- 699 50 E. W. Ozpinar, A. L. Frey, G. Cruse and D. O. Freytes, Tissue Eng. Part B Rev., 2021, 27, 590-603.
- 700 51 J. M. Anderson, J. Mater. Sci. Mater. Med., 2015, **26**, 121.

- 701 52 L. B. Moore and T. R. Kyriakides, Adv. Exp. Med. Biol., 2015, 865, 109-122.
- 702 53 A. J. Pagán and L. Ramakrishnan, Annu. Rev. Immunol., 2018, 36, 639–665.
- 703 T. R. Kyriakides, H. J. Kim, C. Zheng, L. Harkins, W. Tao and E. Deschenes, Biomed. Mater.,, 54 704 DOI:10.1088/1748-605X/ac5574.
- 705 55 A. Dievernich, P. Achenbach, L. Davies and U. Klinge, Hernia, 2022, 26, 309-323.
- 706 56 J. C. Doloff, O. Veiseh, A. J. Vegas, H. H. Tam, S. Farah, M. Ma, J. Li, A. Bader, A. Chiu, A. Sadraei, S. Aresta-707 Dasilva, M. Griffin, S. Jhunjhunwala, M. Webber, S. Siebert, K. Tang, M. Chen, E. Langan, N. Dholokia, R. 708 Thakrar, M. Qi, J. Oberholzer, D. L. Greiner, R. Langer and D. G. Anderson, Nat. Mater., 2017, 16, 671–680.
- 709 57 B. Yang, N. Rutkowski and J. Elisseeff, Biomater. Sci., 2023, 11, 7730–7747.
- 710 58 E. M. Moore, D. R. Maestas, C. C. Cherry, J. A. Garcia, H. Y. Comeau, L. Davenport Huyer, S. H. Kelly, A. N. Peña, R. L. Blosser, G. D. Rosson and J. H. Elisseeff, Sci. Adv., 2021, 7, 1-13. 711
- 712 59 L. Chung, D. R. Maestas, A. Lebid, A. Mageau, G. D. Rosson, X. Wu, M. T. Wolf, A. J. Tam, I. Vanderzee, X. Wang, J. I. Andorko, H. Zhang, R. Narain, K. Sadtler, H. Fan, D. Čiháková, C. J. Le Saux, F. Housseau, D. M. 713 Pardoll and J. H. Elisseeff, Sci. Transl. Med., , DOI:10.1126/scitranslmed.aax3799. 714
- 715 60 J. M. Daley, S. K. Brancato, A. A. Thomay, J. S. Reichner and J. E. Albina, J. Leukoc. Biol., 2009, 87, 59–67.
- 716 F. O. Martinez and S. Gordon, *F1000Prime Rep.*, 2014, **6**, 1–13. 61
- 717 M. E. Ogle, C. E. Segar, S. Sridhar and E. A. Botchwey, Exp. Biol. Med., 2016, 241, 1084-1097. 62
- 718 63 M. Orecchioni, Y. Ghosheh, A. B. Pramod and K. Ley, Front. Immunol., 2019, 10, 1-14.
- 719 64 Y. Shintani, T. Ito, L. Fields, M. Shiraishi, Y. Ichihara, N. Sato, M. Podaru, S. Kainuma, H. Tanaka and K. 720 Suzuki, Sci. Rep., 2017, 7, 1–14.
- 721 65 Y. Liu and T. Segura, Front. Bioeng. Biotechnol., 2020, 8, 1–14.
- 722 66 E. M. O'Brien and K. L. Spiller, J. Leukoc. Biol., 2022, 111, 989-1000.
- 723 F. Heymann, K. T. Von Trotha, C. Preisinger, P. Lynen-Jansen, A. A. Roeth, M. Geiger, L. J. Geisler, A. K. 67 724 Frank, J. Conze, T. Luedde, C. Trautwein, M. Binnebösel, U. P. Neumann and F. Tacke, JCI Insight,
- 725 DOI:10.1172/jci.insight.123862.
- 726 S. K. Wculek, I. Heras-Murillo, A. Mastrangelo, D. Mañanes, M. Galán, V. Miguel, A. Curtabbi, C. Barbas, N. 68
- S. Chandel, J. A. Enríquez, S. Lamas and D. Sancho, Immunity, 2023, 56, 516-530.e9. 727
- 728 69 S.-L. Chen, D. J. Lundy, S.-C. Ruan, H.-C. Chen, Y.-K. Chao, Y.-Y. Cheng, R. P. Prajnamitra, C.-C. Liao, C.-Y. Lin, 729 J. J. Lai and P. C. H. Hsieh, *Biomaterials*, 2022, **289**, 121807.
- 730 70 R. Thibaut, L. Orliaguet, T. Ejlalmanesh, N. Venteclef and F. Alzaid, Front. Immunol., 2022, 13, 918747.
- 731 71 K. E. Martin and A. J. García, *Acta Biomater.*, 2021, **133**, 4–16.
- 732 72 D. G. Barone, A. Carnicer-Lombarte, P. Tourlomousis, R. S. Hamilton, M. Prater, A. L. Rutz, I. B. Dimov, G. G. 733 Malliaras, S. P. Lacour, A. A. B. Robertson, K. Franze, J. W. Fawcett and C. E. Bryant, Proc. Natl. Acad. Sci. U.
- 734 S. A., 2022, **119**, 1–10.
- 735 73 S. D. Sommerfeld, C. Cherry, R. M. Schwab, L. Chung, D. R. Maestas, P. Laffont, J. E. Stein, A. Tam, S.
- 736 Ganguly, F. Housseau, J. M. Taube, D. M. Pardoll, P. Cahan and J. H. Elisseeff, Sci. Immunol.,,
- 737 DOI:10.1126/sciimmunol.aax4783.
- T. Rőszer, Mediators Inflamm., 2015, 2015, 816460. 738 74
- 75 739 A. Viola, F. Munari, R. Sánchez-Rodríguez, T. Scolaro and A. Castegna, Front. Immunol., 2019, 10, 1–16.
- 76 740 S. Willenborg, D. E. Sanin, A. Jais, X. Ding, T. Ulas, J. Nüchel, M. Popović, T. MacVicar, T. Langer, J. L.
- 741 Schultze, A. Gerbaulet, A. Roers, E. J. Pearce, J. C. Brüning, A. Trifunovic and S. A. Eming, Cell Metab., 2021,

- **33**, 2398-2414.e9.
- 77 J. R. Erlich, E. E. To, R. Luong, F. Liong, S. Liong, O. Oseghale, M. A. Miles, S. Bozinovski, R. D. Brooks, R. Vlahos, S. Chan, J. J. O'Leary, D. A. Brooks and S. Selemidis, *Antioxidants*, 2022, **11**, 1488.
- 745 78 J. Huang, J. Xia, L.-L. Huang and Y.-C. Li, Mol. Med. Rep., 2019, 20, 3424–3432.
- 746 79 W. Chou, E. Rampanelli, X. Li and J. P.-Y. Ting, Cell. Mol. Immunol., 2022, 19, 337–351.
- 747 80 R. van der Burgh and M. Boes, *Trends Endocrinol. Metab.*, 2015, **26**, 263–271.
- 748 81 A. Olona, S. Leishman and P. K. Anand, *Trends Immunol.*, 2022, **43**, 978–989.
- E. L. Mills, B. Kelly, A. Logan, A. S. H. Costa, M. Varma, C. E. Bryant, P. Tourlomousis, J. H. M. Däbritz, E.
 Gottlieb, I. Latorre, S. C. Corr, G. McManus, D. Ryan, H. T. Jacobs, M. Szibor, R. J. Xavier, T. Braun, C. Frezza,
 M. P. Murphy and L. A. O'Neill, *Cell*, 2016, **167**, 457-470.e13.
- 752 83 F. Wang, S. Zhang, I. Vuckovic, R. Jeon, A. Lerman, C. D. Folmes, P. P. Dzeja and J. Herrmann, *Cell Metab.*, 2018, **28**, 463-475.e4.
- 754 84 G. Caputa, L. J. Flachsmann and A. M. Cameron, *Immunol. Cell Biol.*, 2019, **97**, 268–278.
- 755 85 J.-H. Shi, H. Guan, S. Shi, W.-X. Cai, X.-Z. Bai, X.-L. Hu, X.-B. Fang, J.-Q. Liu, K. Tao, X.-X. Zhu, C.-W. Tang and D.-H. Hu, *Arch. Dermatol. Res.*, 2013, **305**, 341–352.
- 757 86 Y. Zhu, X. Zhang, S. Xie, W. Bao, J. Chen, Q. Wu, X. Lai, L. Liu, S. Xiong and Y. Peng, *Immunology*, 2022, **167**, 758 576–589.
- B. Dang, Q. Gao, L. Zhang, J. Zhang, H. Cai, Y. Zhu, Q. Zhong, J. Liu, Y. Niu, K. Mao, N. Xiao, W.-H. Liu, S. Lin,
 J. Huang, S. C.-C. Huang, P.-C. Ho and S.-C. Cheng, *Cell Rep.*, 2023, 42, 112471.
- 761 88 R. Klopfleisch, Acta Biomater., 2016, **43**, 3–13.
- 762 89 J. C. White, Z. L. Jiang, M. P. Diamond and G. M. Saed, Fertil. Steril., 2011, **96**, 758-763.e3.
- 763 90 M. Ueno, T. Maeno, M. Nomura, K. Aoyagi-Ikeda, H. Matsui, K. Hara, T. Tanaka, T. Iso, T. Suga and M. Kurabayashi, *Am. J. Physiol. Cell. Mol. Physiol.*, 2011, **300**, L740–L752.
- 765 91 K. Nakagome, M. Dohi, K. Okunishi, R. Tanaka, J. Miyazaki and J. Yamamoto, *Thorax*, 2006, **61**, 886–894.
- 766 92 K. M. DeFife, C. R. Jenney, A. K. McNally, E. Colton and J. M. Anderson, J. Immunol., 1997, **158**, 3385–90.
- 767 93 A. K. McNally and J. M. Anderson, Am. J. Pathol., 1995, 147, 1487–99.
- R. Milde, J. Ritter, G. A. Tennent, A. Loesch, F. O. Martinez, S. Gordon, M. B. Pepys, A. Verschoor and L. Helming, *Cell Rep.*, 2015, **13**, 1937–1948.
- 770 95 K. Ahmadzadeh, M. Vanoppen, C. D. Rose, P. Matthys and C. H. Wouters, *Front. Cell Dev. Biol.*, 2022, **10**, 1–771 22.
- 772 96 F. Eslami-Kaliji, N. Hedayat Nia, J. R. T. Lakey, A. M. Smink and M. Mohammadi, *Polymers (Basel).*, 2023, **15**, 1313.
- J. Koopsen, S. M. Van Putten, H. Van Veen, D. I. Picavet, T. J. De Vries, R. A. Bank and V. Everts, *J. Struct. Biol.*, 2016, **195**, 31–40.
- 776 98 R. J. Miron and D. D. Bosshardt, *Tissue Eng. Part B Rev.*, 2018, **24**, 53–65.
- 777 99 P. J. Brooks, M. Glogauer and C. A. McCulloch, Am. J. Pathol., 2019, 189, 1145–1158.
- 778 100 Z. Sheikh, P. J. Brooks, O. Barzilay, N. Fine and M. Glogauer, *Materials (Basel).*, 2015, **8**, 5671–5701.
- 779 101 O. Dufrançais, R. Mascarau, R. Poincloux, I. Maridonneau-Parini, B. Raynaud-Messina and C. Vérollet, *Cell. Mol. Life Sci.*, 2021, **78**, 6087–6104.
- 781 102 J. Takito and M. Nakamura, *Int. J. Mol. Sci.*, 2020, **21**, 6629.

- 782 103 A. K. McNally and J. M. Anderson, in *Cell Fusion in Health and Disease*, 2011, vol. 5, pp. 97–111.
- L. Herrtwich, I. Nanda, K. Evangelou, T. Nikolova, V. Horn, Sagar, D. Erny, J. Stefanowski, L. Rogell, C. Klein,
 K. Gharun, M. Follo, M. Seidl, B. Kremer, N. Münke, J. Senges, M. Fliegauf, T. Aschman, D. Pfeifer, S.
- Sarrazin, M. H. Sieweke, D. Wagner, C. Dierks, T. Haaf, T. Ness, M. M. Zaiss, R. E. Voll, S. D. Deshmukh, M.
- Prinz, T. Goldmann, C. Hölscher, A. E. Hauser, A. J. Lopez-Contreras, D. Grün, V. Gorgoulis, A. Diefenbach, P.
- 787 Henneke and A. Triantafyllopoulou, *Cell*, 2016, **167**, 1264-1280.e18.
- 788 105 A. Rodriguez, S. R. MacEwan, H. Meyerson, J. T. Kirk and J. M. Anderson, *J. Biomed. Mater. Res. Part A*, 2009, **90A**, 106–113.
- 790 106 A. K. McNally and J. M. Anderson, J. Biomed. Mater. Res. Part A, 2015, 103, 1380–1390.
- 791 107 J. J. A. McLeod, B. Baker and J. J. Ryan, *Cytokine*, 2015, **75**, 57–61.
- 792 108 J. Yang, B. Jao, A. K. McNally and J. M. Anderson, J. Biomed. Mater. Res. Part A, 2014, 102, 2017–2023.
- 793 109 A. K. McNally and J. M. Anderson, Exp. Mol. Pathol., 2011, **91**, 673–681.
- 794 110 R. Goswami, R. K. Arya, S. Sharma, B. Dutta, D. R. Stamov, X. Zhu and S. O. Rahaman, *Sci. Signal.*, , DOI:10.1126/SCISIGNAL.ABD4077.
- 796 111 J. M. Anderson, K. Defife, A. Mcnally, T. Collier and C. Jenney, *J. Mater. Sci. Mater. Med.*, 1999, **10**, 579–588.
- 798 112 S. N. Christo, K. R. Diener, J. Manavis, M. A. Grimbaldeston, A. Bachhuka, K. Vasilev and J. D. Hayball, *Sci. Rep.*, 2016, **6**, 1–14.
- 800 113 L. A. McKiel, K. A. Woodhouse and L. E. Fitzpatrick, MRS Commun., 2020, 10, 55–68.
- 801 114 G. Zhou and T. Groth, *Macromol. Biosci.*, 2018, **18**, 1–15.
- 802 115 Y.-S. Kim, S. Shin, E. J. Choi, S. W. Moon, C. K. Jung, Y.-J. Chung and S. H. Lee, *J. Invest. Dermatol.*, 2022, **2**, 803 1–16.
- 804 116 L. A. McKiel and L. E. Fitzpatrick, ACS Biomater. Sci. Eng., 2018, 4, 3792–3801.
- 805 117 Q. H. Zhao, J. M. Anderson, A. Hiltner, G. A. Lodoen and C. R. Payet, *J. Biomed. Mater. Res.*, 1992, **26**, 1019–806 1038.
- 807 118 S. Chen, J. A. Jones, Y. Xu, H.-Y. Low, J. M. Anderson and K. W. Leong, *Biomaterials*, 2010, **31**, 3479–3491.
- W. G. Brodbeck, J. Patel, G. Voskerician, E. Christenson, M. S. Shive, Y. Nakayama, T. Matsuda, N. P. Ziats and J. M. Anderson, *Proc. Natl. Acad. Sci. U. S. A.*, 2002, **99**, 10287–10292.
- 810 120 S. Mezouar, M. Katsogiannou, A. Ben Amara, F. Bretelle and J.-L. Mege, Placenta, 2021, 103, 94–103.
- 811 121 L. Reyes and T. G. Golos, *Front. Immunol.*, 2018, **9**, 1–8.
- 812 122 Y. Ma, Y. Ye, J. Zhang, C. C. Ruan and P. J. Gao, Med. (United States), 2019, 98, 1–6.
- 813 123 M. B. Buechler, W. Fu and S. J. Turley, *Immunity*, 2021, **54**, 903–915.
- 814 124 S. Van Linthout, K. Miteva and C. Tschöpe, *Cardiovasc. Res.*, 2014, **102**, 258–269.
- 815 125 Y. Li, J. Zhao, Y. Yin, K. Li, C. Zhang and Y. Zheng, Int. J. Biol. Sci., 2022, 18, 5405–5414.
- 816 126 R. M. Gallucci, E. G. Lee and J. J. Tomasek, J. Invest. Dermatol., 2006, **126**, 561–568.
- 817 127 N. Takamura, L. Renaud, W. A. da Silveira and C. Feghali-Bostwick, Front. Immunol., 2021, 12.
- 818 T. A. Wynn and L. Barron, Semin. Liver Dis., 2010, **30**, 245–257.
- 819 129 A. L. Theiss, J. G. Simmons, C. Jobin and P. K. Lund, *J. Biol. Chem.*, 2005, **280**, 36099–36109.
- 820 130 L. S. Verjee, J. S. N. Verhoekx, J. K. K. Chan, T. Krausgruber, V. Nicolaidou, D. Izadi, D. Davidson, M.

- Feldmann, K. S. Midwood and J. Nanchahal, *Proc. Natl. Acad. Sci.*, , DOI:10.1073/pnas.1301100110.
- 822 131 M. Kolb, P. J. Margetts, D. C. Anthony, F. Pitossi and J. Gauldie, J. Clin. Invest., 2001, 107, 1529–1536.
- 823 132 M. M. Mia, M. Boersema and R. A. Bank, *PLoS One*, 2014, **9**, e91559.
- 824 133 J. C. Bonner, Cytokine Growth Factor Rev., 2004, **15**, 255–273.
- 825 134 D. H. Kim, Y. S. Song, S. Y. Song and C. H. Kim, Arch. Aesthetic Plast. Surg., 2016, 22, 129.
- 826 135 U. Klueh, D. I. Dorsky and D. L. Kreutzer, *Biomaterials*, 2005, **26**, 1155–1163.
- 827 136 W. K. Ward, J. Diabetes Sci. Technol., 2008, 2, 768–777.
 - 137 M. Giannandrea and W. C. Parks, *Dis. Model. Mech.*, 2014, **7**, 193–203.
- 829 138 A. S. Caldwell, V. V. Rao, A. C. Golden, D. J. Bell, J. C. Grim and K. S. Anseth, *Bioeng. Transl. Med.*, 2021, **6**, 830 1–13.
- 831 139 T. Truong and K. S. Jones, J. Biomed. Mater. Res. Part A, 2018, 106, 2424–2432.
- D. T. Luttikhuizen, M. J. van Amerongen, P. C. de Feijter, A. H. Petersen, M. C. Harmsen and M. J. A. van Luyn, *Biomaterials*, 2006, **27**, 5763–5770.
- T. Whitehead-Clarke, R. Karanjia, J. Banks, V. Beynon, S. Parker, D. Sanders, V. Mudera, A. Windsor and A. Kureshi, *Hernia*, 2022, **26**, 297–307.
- G. Pascual, M. Rodríguez, B. Pérez-Köhler, S. Benito-Martínez, B. Calvo, F. García-Moreno and J. M. Bellón,
 Hernia, 2020, 24, 1159–1173.
- 838 143 R. Liang, A. Fisk, G. King, L. Meyn, X. Xiao and P. Moalli, *Acta Biomater.*, 2022, **143**, 310–319.
- 839 144 A. M. Artsen, M. Rytel, R. Liang, G. E. King, L. Meyn, S. D. Abramowitch and P. A. Moalli, *Acta Biomater.*, 840 2019, **96**, 203–210.
- 145 E. E. Anderson, E. Perilli, C. J. Carati and K. J. Reynolds, *J. Biomed. Mater. Res. B. Appl. Biomater.*, 2017, **105**,
 1447–1452.
- 843 146 M. Kastellorizios, F. Papadimitrakopoulos and D. J. Burgess, J. Control. Release, 2015, 202, 101–107.
- A. J. Vegas, O. Veiseh, J. C. Doloff, M. Ma, H. H. Tam, K. Bratlie, J. Li, A. R. Bader, E. Langan, K. Olejnik, P.
 Fenton, J. W. Kang, J. Hollister-Locke, M. A. Bochenek, A. Chiu, S. Siebert, K. Tang, S. Jhunjhunwala, S.
 Aresta-Dasilva, N. Dholakia, R. Thakrar, T. Vietti, M. Chen, J. Cohen, K. Siniakowicz, M. Qi, J. McGarrigle, S.
 Lyle, D. M. Harlan, D. L. Greiner, J. Oberholzer, G. C. Weir, R. Langer and D. G. Anderson, *Nat. Biotechnol.*,
 2016, 34, 345–352.
- 849 148 K. Sadtler and J. H. Elisseeff, *Biomater. Sci.*, 2019, **7**, 4472–4481.
- C. Cherry, J. I. Andorko, K. Krishnan, J. C. Mejías, H. H. Nguyen, K. B. Stivers, E. F. Gray-Gaillard, A. Ruta, J.
 Han, N. Hamada, M. Hamada, I. Sturmlechner, S. Trewartha, J. H. Michel, L. Davenport Huyer, M. T. Wolf,
 A. J. Tam, A. N. Peña, S. Keerthivasan, C. J. Le Saux, E. J. Fertig, D. J. Baker, F. Housseau, J. M. van Deursen,
 D. M. Pardoll and J. H. Elisseeff, *GeroScience*, 2023, 45, 2559–2587.
- T. Krausgruber, A. Redl, D. Barreca, K. Doberer, D. Romanovskaia, L. Dobnikar, M. Guarini, L.
 Unterluggauer, L. Kleissl, D. Atzmüller, C. Mayerhofer, A. Kopf, S. Saluzzo, C. X. Lim, P. Rexie, T. Weichhart,
 C. Bock and G. Stary, *Immunity*, 2023, 56, 289-306.e7.
- 857 151 E. M. Moore, D. R. Maestas, H. Y. Comeau and J. H. Elisseeff, *Tissue Eng. Part B Rev.*, 2021, **27**, 39–47.
- 858 152 L. S. Saleh and S. J. Bryant, *Drug Discov. Today Dis. Model.*, 2017, **24**, 13–21.
- H. M. Rostam, L. E. Fisher, A. L. Hook, L. Burroughs, J. C. Luckett, G. P. Figueredo, C. Mbadugha, A. C. K. Teo,
 A. Latif, L. Kämmerling, M. Day, K. Lawler, D. Barrett, S. Elsheikh, M. Ilyas, D. A. Winkler, M. R. Alexander
 and A. M. Ghaemmaghami, *Matter*, 2020, 2, 1564–1581.

862	154	K P Robb I Audet R Gandhiand S	. Viswanathan. <i>Front. Immunol.</i> . 2022. 13 . 1–2
802	154	R. P. RODD. J. AUGEL. R. Gangni and S	. VISWANALNAN, <i>Front. Immunoi.</i> . 2022. 13

- K. E. de Goede, K. J. Harber, F. S. Gorki, S. G. S. Verberk, L. A. Groh, E. D. Keuning, E. A. Struys, M. van
 Weeghel, A. Haschemi, M. P. J. de Winther, X. A. M. H. van Dierendonck and J. Van den Bossche, *Biochim. Biophys. Acta Mol. Basis Dis.*, 2022, **1868**, 166427.
- 866 156 S. Koo, B. Szczesny, X. Wan, N. Putluri and N. J. Garg, Front. Immunol., , DOI:10.3389/fimmu.2018.00202.
- 867 157 R. J. Argüello, A. J. Combes, R. Char, J.-P. Gigan, A. I. Baaziz, E. Bousiquot, V. Camosseto, B. Samad, J. Tsui,
 R. J. Argüello, A. J. Combes, R. Char, J.-P. Gigan, A. I. Baaziz, E. Bousiquot, V. Camosseto, B. Samad, J. Tsui,
 R. J. Argüello, A. J. Combes, R. Char, J.-P. Gigan, A. I. Baaziz, E. Bousiquot, V. Camosseto, B. Samad, J. Tsui,
 R. J. Argüello, A. J. Combes, R. Char, J.-P. Gigan, A. I. Baaziz, E. Bousiquot, V. Camosseto, B. Samad, J. Tsui,
 R. J. Argüello, A. J. Combes, R. Char, J.-P. Gigan, A. I. Baaziz, E. Bousiquot, V. Camosseto, B. Samad, J. Tsui,
 R. J. Argüello, A. J. Combes, R. Char, J.-P. Gigan, A. I. Baaziz, E. Bousiquot, V. Camosseto, B. Samad, J. Tsui,
 R. J. Argüello, A. J. Combes, R. Char, J.-P. Gigan, A. I. Baaziz, E. Bousiquot, V. Camosseto, B. Samad, J. Tsui,
 R. J. Argüello, A. J. Combes, R. Char, J.-P. Gigan, A. I. Baaziz, E. Bousiquot, V. Camosseto, B. Samad, J. Tsui,
 R. J. Argüello, A. J. Combes, R. Char, J.-P. Gigan, A. I. Baaziz, E. Bousiquot, V. Camosseto, B. Samad, J. Tsui,
 R. J. Argüello, A. J. Combes, R. Char, J.-P. Gigan, A. I. Baaziz, E. Bousiquot, V. Camosseto, B. Samad, J. Tsui,
 R. J. Argüello, A. J. Combes, R. Char, J.-P. Gigan, A. I. Baaziz, E. Bousiquot, V. Camosseto, B. Samad, J. Tsui,
 R. J. Argüello, A. J. Combes, R. Char, J.-P. Gigan, A. I. Baaziz, E. Bousiquot, V. Camosseto, B. Samad, J. Tsui,
 R. J. Argüello, A. J. Combes, R. Char, J. Char, J. Char, J. Char, L. C
- L. R. Pelgrom, G. M. Davis, S. O'Shaughnessy, E. J. M. Wezenberg, S. I. Van Kasteren, D. K. Finlay and L. V. Sinclair, *Cell Rep.*, 2023, **42**, 112828.
- R. J. W. Arts, B. Novakovic, R. ter Horst, A. Carvalho, S. Bekkering, E. Lachmandas, F. Rodrigues, R. Silvestre,
 S. C. Cheng, S. Y. Wang, E. Habibi, L. G. Gonçalves, I. Mesquita, C. Cunha, A. van Laarhoven, F. L. van de
 Veerdonk, D. L. Williams, J. W. M. van der Meer, C. Logie, L. A. O'Neill, C. A. Dinarello, N. P. Riksen, R. van
 Crevel, C. Clish, R. A. Notebaart, L. A. B. Joosten, H. G. Stunnenberg, R. J. Xavier and M. G. Netea, *Cell Metab.*, 2016, 24, 807–819.
- S. Bekkering, R. J. W. Arts, B. Novakovic, I. Kourtzelis, C. D. C. C. van der Heijden, Y. Li, C. D. Popa, R. ter Horst, J. van Tuijl, R. T. Netea-Maier, F. L. van de Veerdonk, T. Chavakis, L. A. B. Joosten, J. W. M. van der Meer, H. Stunnenberg, N. P. Riksen and M. G. Netea, *Cell*, 2018, **172**, 135-146.e9.
- 880 161 A. Gavlin, A. S. Kierans, J. Chen, C. Song, P. Guniganti and F. S. Mazzariol, Radiographics, 2020, 40, 432–453.
- 881 162 S. Capuani, G. Malgir, C. Y. X. Chua and A. Grattoni, Bioeng. Transl. Med., 2022, 1–22.
- 882 163 E. N. Zhang, J. Clément, A. Alameri, A. Ng, T. E. Kennedy and D. Juncker, *Adv. Mater. Technol.*, , DOI:10.1002/admt.202000909.
- 884 164 N. O. Monteiro, M. R. Casanova, J. F. Fangueiro, R. L. Reis and N. M. Neves, *Biomed. Mater.*, 2023, **18**, 035008.
- F. Robotti, S. Bottan, F. Fraschetti, A. Mallone, G. Pellegrini, N. Lindenblatt, C. Starck, V. Falk, D. Poulikakos and A. Ferrari, *Sci. Rep.*, 2018, **8**, 10887.
- 888 166 E. A. Vogler, Biomaterials, 2012, **33**, 1201–1237.
- 889 167 L.-C. Xu and C. A. Siedlecki, *Biomaterials*, 2007, **28**, 3273–3283.
- 890 168 R. M. Shelton, A. C. Rasmussen and J. E. Davies, *Biomaterials*, 1988, **9**, 24–29.
- P. Pakshir, M. Alizadehgiashi, B. Wong, N. M. Coelho, X. Chen, Z. Gong, V. B. Shenoy, C. A. McCulloch and B.
 Hinz, Nat. Commun., 2019, 10, 1850.
- 893 170 C. Tanasescu, A. Moisin, A. Mihetiu, D. Serban, A. Costache and D. Bratu, Exp. Ther. Med., 2021, 22, 1–6.
- 894 171 J. L. Frodel M and S. Lee, Arch. Otolaryngol. Head Neck Surg., 1998, **124**, 1219–1223.
- 895 172 H. Park, J. W. Choi and W. S. Jeong, *J. Craniofac. Surg.*, 2022, **33**, 1394–1399.
- 896 173 M. J. R. Virlan, D. Miricescu, A. Totan, M. Greabu, C. Tanase, C. M. Sabliov, C. Caruntu and B. Calenic, *J. Chem.*, , DOI:10.1155/2015/525832.
- T. Weigel, T. Schmitz, T. Pfister, S. Gaetzner, M. Jannasch, R. Al-Hijailan, S. Schürlein, S. Suliman, K. Mustafa and J. Hansmann, *Sci. Rep.*, 2018, **8**, 14545.
- F. Santanelli di Pompeo, M. Sorotos, M. W. Clemens, G. Firmani, E. Athanasopoulos, K. Arctander, B.
 Berenguer, K. Bozikov, A. Cardoso, Å. E. Nord, C. Filip, A. Georgeskou Romania, C. Heitman, O. Kaarela, M.
 Kolenda, M. Hamdi, L. Lantieri, D. Lumenta, N. Mercer, E. Ruegg, F. Santanelli di Pompeo, Z. Stanec, R. Van
 Der Hulst and J. J. Vranckx, *Aesthetic Surg. J.*, 2021, 41, 1014–1025.

- 904 176 E. B. Lynch, R. C. DeCoster, K. S. Vyas, B. D. Rinker, M. Yang, H. C. Vasconez and M. W. Clemens, *Ann. Breast Surg.*, 2021, **5**, 30–30.
- 906 177 N. Castel, T. Soon-Sutton, P. Deptula, A. Flaherty and F. D. Parsa, Arch. Plast. Surg., 2015, 42, 186–193.
- 907 178 N. G. Welch, D. A. Winkler and H. Thissen, Adv. Drug Deliv. Rev., 2020, 167, 109–120.
- 908 179 D. Dong, C. Tsao, H. C. Hung, F. Yao, C. Tang, L. Niu, J. Ma, J. MacArthur, A. Sinclair, K. Wu, P. Jain, M. R. Hansen, D. Ly, S. G. H. Tang, T. M. Luu, P. Jain and S. Jiang, *Sci. Adv.*, 2021, **7**, 1–10.
- 910 180 L. Zhang, Z. Cao, T. Bai, L. Carr, J.-R. Ella-Menye, C. Irvin, B. D. Ratner and S. Jiang, *Nat. Biotechnol.*, 2013, 911 **31**, 553–556.
- 912 181 D. Faulón Marruecos, L. S. Saleh, H. H. Kim, S. J. Bryant, D. K. Schwartz and J. L. Kaar, *ACS Appl. Bio Mater.*,
 913 2019, 4698–4702.
- 914 182 K. Burugapalli, S. Wijesuriya, N. Wang and W. Song, J. Biomed. Mater. Res. Part A, 2018, 106, 1072–1081.
- 915 183 S. M. Ruppert, T. R. Hawn, A. Arrigoni, T. N. Wight and P. L. Bollyky, *Immunol. Res.*, 2014, **58**, 186–192.
- 916 184 H. AlKhoury, A. Hautmann, F. Erdmann, G. Zhou, S. Stojanović, S. Najman and T. Groth, *J. Biomed. Mater.* 917 *Res. Part A*, 2020, **108**, 1099–1111.
- 918 S. Hu, F. D. Martinez-Garcia, B. N. Moeun, J. K. Burgess, M. C. Harmsen, C. Hoesli and P. de Vos, *Mater. Sci. Eng. C*, 2021, **123**, 112009.
- 920 186 S. Mukherjee, B. Kim, L. Y. Cheng, M. D. Doerfert, J. Li, A. Hernandez, L. Liang, M. I. Jarvis, P. D. Rios, S.
 921 Ghani, I. Joshi, D. Isa, T. Ray, T. Terlier, C. Fell, P. Song, R. N. Miranda, J. Oberholzer, D. Y. Zhang and O.
 922 Veiseh, *Nat. Biomed. Eng.*, , DOI:10.1038/s41551-023-01016-2.
- 923 187 D. A. Alagpulinsa, J. J. L. Cao, R. K. Driscoll, R. F. Sîrbulescu, M. F. E. Penson, M. Sremac, E. N. Engquist, T. A. Brauns, J. F. Markmann, D. A. Melton and M. C. Poznansky, *Am. J. Transplant.*, 2019, **19**, 1930–1940.
- 925 188 R. P. Tan, N. Hallahan, E. Kosobrodova, P. L. Michael, F. Wei, M. Santos, Y. T. Lam, A. H. P. Chan, Y. Xiao, M. M. M. Bilek, P. Thorn and S. G. Wise, *ACS Appl. Mater. Interfaces*, 2020, **12**, 56908–56923.
- 927 189 A. E. Anderson, I. Wu, A. J. Parrillo, M. T. Wolf, D. R. Maestas, I. Graham, A. J. Tam, R. M. Payne, J. Aston, C. M. Cooney, P. Byrne, D. S. Cooney and J. H. Elisseeff, *npj Regen. Med.*, 2022, **7**, 6.
- 929 190 J. S. Lewis, K. Roy and B. G. Keselowsky, MRS Bull., 2014, **39**, 25–34.
- 191 L. W. Norton, H. E. Koschwanez, N. A. Wisniewski, B. Klitzman and W. M. Reichert, *J. Biomed. Mater. Res.* 931 *Part A*, 2007, **81A**, 858–869.
- 932 192 Y. Zhong and R. V. Bellamkonda, *Brain Res.*, 2007, **1148**, 15–27.
- 933 193 K. Battiston, I. Parrag, M. Statham, D. Louka, H. Fischer, G. Mackey, A. Daley, F. Gu, E. Baldwin, B. Yang, B. Muirhead, E. A. Hicks, H. Sheardown, L. Kalachev, C. Crean, J. Edelman, J. P. Santerre and W. Naimark, *Nat. Commun.*, 2021, **12**, 1–17.
- 936 194 J. C. Quarterman, S. M. Geary and A. K. Salem, *Eur. J. Pharm. Biopharm.*, 2021, **159**, 21–35.
- 937 195 J. D. Weaver, Y. Song, E. Y. Yang, C. Ricordi, A. Pileggi, P. Buchwald and C. L. Stabler, *Tissue Eng. Part A*,
 938 2015, 21, 2250–2261.
- 939 196 P. Pakshir, F. Younesi, K.-A. Wootton, K. Battiston, G. Whitton, B. Ilagan, D. Louka, M. Statham, G. Mackey, 940 A. Daley, I. Parrag, W. Naimark and B. Hinz, *Biomaterials*, 2022, **286**, 121586.
- J. A. W. Polderman, V. Farhang-Razi, S. van Dieren, P. Kranke, J. H. DeVries, M. W. Hollmann, B. Preckel and
 J. Hermanides, *Anaesthesia*, 2019, **74**, 929–939.
- 943 198 L. Nabai, A. Ghahary and J. Jackson, *Bioengineering*, 2023, **10**, 298.
- 944 199 A. Fayzullin, S. Churbanov, N. Ignatieva, O. Zakharkina, M. Tokarev, D. Mudryak, Y. Khristidis, M. Balyasin,

- 945 A. Kurkov, E. N. Golubeva, N. A. Aksenova, T. Dyuzheva, P. Timashev, A. Guller and A. Shekhter, 946 *Biomedicines*, 2021, **9**, 853.
- 947 200 B. S. Jeon, B. H. Shin, B. K. Huh, B. H. Kim, S.-N. Kim, H. B. Ji, S. H. Lee, S. I. Kang, J. H. Shim, S. M. Kang, J. C.
 948 Lee, K. S. Lee, C. Y. Heo and Y. Bin Choy, *J. Ind. Eng. Chem.*, 2018, 63, 168–180.
- 949 201 S.-Y. Nam, H. B. Ji, B. H. Shin, P. N. Chien, N. Donmez, X. R. Zhang, B. K. Huh, M. J. Kim, Y. Bin Choy and C. Y. Heo, *Materials (Basel).*, 2021, **14**, 3917.
- 951 202 W. Li, B. He, W. Dai, Q. Zhang and Y. Liu, Int. Ophthalmol., 2014, 34, 465–476.
- 952 203 S. Park, M. Park, B. H. Kim, J. E. Lee, H. J. Park, S. H. Lee, C. G. Park, M. H. Kim, R. Kim, E. H. Kim, C. Y. Heo and Y. Bin Choy, *J. Control. Release*, 2015, **200**, 125–137.
- 954 204 L. Nabai, A. Ghahary and J. Jackson, *Pharmaceutics*, 2022, **14**, 1546.
- 955 205 S. Farah, J. C. Doloff, P. Müller, A. Sadraei, H. J. Han, K. Olafson, K. Vyas, H. H. Tam, J. Hollister-Lock, P. S. Kowalski, M. Griffin, A. Meng, M. McAvoy, A. C. Graham, J. McGarrigle, J. Oberholzer, G. C. Weir, D. L. Greiner, R. Langer and D. G. Anderson, *Nat. Mater.*, 2019, **18**, 892–904.
- 958 206 M. Duvvuri, K. Motz, M. Murphy, M. Feeley, D. Ding, A. Lee, J. H. Elisseeff and A. T. Hillel, *Biomater. Sci.*, 959 2019, **7**, 1863–1874.
- 960 207 K. M. Motz, I. A. Lina, I. Samad, M. K. Murphy, M. Duvvuri, R. J. Davis, A. Gelbard, L. Chung, Y. Chan-Li, S. Collins, J. D. Powell, J. H. Elisseeff, M. R. Horton and A. T. Hillel, *JCl Insight*, DOI:10.1172/jci.insight.158456.
- 962 208 D. Hachim, S. T. LoPresti, C. C. Yates and B. N. Brown, *Biomaterials*, 2017, **112**, 95–107.
- D. R. Maestas, L. Chung, J. Han, X. Wang, S. D. Sommerfeld, S. H. Kelly, E. Moore, H. H. Nguyen, J. C. Mejías,
 A. N. Peña, H. Zhang, J. S. T. Hooks, A. F. Chin, J. I. Andorko, C. A. Berlinicke, K. Krishnan, Y. Choi, A. E.
 Anderson, R. Mahatme, C. Mejia, M. Eric, J. Woo, S. Ganguly, D. J. Zack, L. Zhao, E. J. Pearce, F. Housseau,
 D. M. Pardoll and J. H. Elisseeff, *Proc. Natl. Acad. Sci.*, DOI:10.1073/pnas.2211703120.
- 967 210 M. Dragovic, M. Pejovic, J. Stepic, S. Colic, B. Dozic, S. Dragovic, M. Lazarevic, N. Nikolic, J. Milasin and B. Milicic, *Clin. Oral Investig.*, 2020, **24**, 1527–1541.
- 969 211 F. Selvi, S. Cakarer, T. Can, S. İ. Kirli Topcu, A. Palancioglu, B. Keskin, B. Bilgic, M. Yaltirik and C. Keskin, *J. Istanbul Univ. Fac. Dent.*, 2016, **50**, 35–42.
- 971 212 M. Alves de Oliveira, A. Arcanjo, F. Castro, J. C. Fernandes and G. V Fernandes, Surgeries, 2024, 5, 350–366.
- F. Köckerling, N. N. Alam, S. A. Antoniou, I. R. Daniels, F. Famiglietti, R. H. Fortelny, M. M. Heiss, F.
 Kallinowski, I. Kyle-Leinhase, F. Mayer, M. Miserez, A. Montgomery, S. Morales-Conde, F. Muysoms, S. K.
 Narang, A. Petter-Puchner, W. Reinpold, H. Scheuerlein, M. Smietanski, B. Stechemesser, C. Strey, G.
 Woeste and N. J. Smart, *Hernia*, 2018, 22, 249–269.
- 976 214 S. Trippoli, E. Caccese, G. Tulli, P. Ipponi, C. Marinai and A. Messori, Int. J. Surg., 2018, **52**, 278–284.
- 977 215 S. K. Kamarajah, S. J. Chapman, J. Glasbey, D. Morton, N. Smart, T. Pinkney and A. Bhangu, *BJS Open*, 2018, 978 **2**, 371–380.
- 979 216 F. Köckerling, N. N. Alam, S. K. Narang, I. R. Daniels and N. J. Smart, *Front. Surg.*, 2015, **2**, 1–5.
- 980 217 G. Passot, J. Margier, A. Kefleyesus, P. Rousset, P. Ortega-Deballon, Y. Renard, S. Bin and L. Villeneuve, *BMJ Open*, 2022, **12**, e061184.
- 982 218 U. Klinge, B. Klosterhalfen, M. Müller and V. Schumpelick, Eur. J. Surg., 1999, 165, 665–673.
- 983 219 S. Öberg, K. Andresen and J. Rosenberg, Surg. Innov., 2017, **24**, 289–298.
- 984 220 J. Henderson and S. O'Reilly, *Trends Endocrinol. Metab.*, 2021, **32**, 639–653.
- A. Hooftman, C. G. Peace, D. G. Ryan, E. A. Day, M. Yang, A. F. McGettrick, M. Yin, E. N. Montano, L. Huo, J.
 E. Toller-Kawahisa, V. Zecchini, T. A. J. Ryan, A. Bolado-Carrancio, A. M. Casey, H. A. Prag, A. S. H. Costa, G.

- De Los Santos, M. Ishimori, D. J. Wallace, S. Venuturupalli, E. Nikitopoulou, N. Frizzell, C. Johansson, A. Von Kriegsheim, M. P. Murphy, C. Jefferies, C. Frezza and L. A. J. O'Neill, *Nature*, , DOI:10.1038/s41586-023-05720-6.
- 990 222 C. Diskin, A. Zotta, S. E. Corcoran, V. J. Tyrrell, Z. Zaslona, V. B. O'Donnell and L. A. J. O'Neill, *J. Immunol.*, 991 2021, **207**, 2561–2569.
- 992 223 M. D. Kornberg, P. Bhargava, P. M. Kim, V. Putluri, A. M. Snowman, N. Putluri, P. A. Calabresi and S. H. Snyder, *Science (80-.).*, 2018, **360**, 449–453.
- 994 224 D. G. Ryan, M. P. Murphy, C. Frezza, H. A. Prag, E. T. Chouchani, L. A. O'Neill and E. L. Mills, *Nat. Metab.*, 995 2019, **1**, 16–33.
- 996 225 D. G. Ryan and L. A. J. O'Neill, *Annu. Rev. Immunol.*, 2020, **38**, 289–313.
- 997 226 L. A. J. O'Neill and M. N. Artyomov, *Nat. Rev. Immunol.*, 2019, **19**, 273–281.
- 998 227 C. G. Peace and L. A. J. O'Neill, *J. Clin. Invest.*, , DOI:10.1172/JCI148548.
- 999 228 J. Lin, J. Ren, D. S. Gao, Y. Dai and L. Yu, Front. Chem., , DOI:10.3389/fchem.2021.669308.
- 1000 229 J. Shi and C. Cai, Front. Immunol., 2022, **13**, 1–9.
- W. He, A. Henne, M. Lauterbach, E. Geißmar, F. Nikolka, C. Kho, A. Heinz, C. Dostert, M. Grusdat, T. Cordes,
 J. Härm, O. Goldmann, A. Ewen, C. Verschueren, J. Blay-Cadanet, R. Geffers, H. Garritsen, M. Kneiling, C. K.
 Holm, C. M. Metallo, E. Medina, Z. Abdullah, E. Latz, D. Brenner and K. Hiller, *Nat. Metab.*, 2022, 4, 524–
 533.
- 1005 231 F. Chen, W. A. M. Elgaher, M. Winterhoff, K. Büssow, F. H. Waqas, E. Graner, Y. Pires-Afonso, L. Casares
 1006 Perez, L. de la Vega, N. Sahini, L. Czichon, W. Zobl, T. Zillinger, M. Shehata, S. Pleschka, H. Bähre, C. Falk, A.
 1007 Michelucci, S. Schuchardt, W. Blankenfeldt, A. K. H. Hirsch and F. Pessler, *Nat. Metab.*, 2022, 4, 534–546.
- M. Bambouskova, L. Gorvel, V. Lampropoulou, A. Sergushichev, E. Loginicheva, K. Johnson, D. Korenfeld,
 M. E. Mathyer, H. Kim, L.-H. Huang, D. Duncan, H. Bregman, A. Keskin, A. Santeford, R. S. Apte, R. Sehgal, B.
 Johnson, G. K. Amarasinghe, M. P. Soares, T. Satoh, S. Akira, T. Hai, C. de Guzman Strong, K. Auclair, T. P.
 Roddy, S. A. Biller, M. Jovanovic, E. Klechevsky, K. M. Stewart, G. J. Randolph and M. N. Artyomov, *Nature*,
 2018, 556, 501–504.
- E. L. Mills, D. G. Ryan, H. A. Prag, D. Dikovskaya, D. Menon, Z. Zaslona, M. P. Jedrychowski, A. S. H. Costa,
 M. Higgins, E. Hams, J. Szpyt, M. C. Runtsch, M. S. King, J. F. McGouran, R. Fischer, B. M. Kessler, A. F.
 McGettrick, M. M. Hughes, R. G. Carroll, L. M. Booty, E. V. Knatko, P. J. Meakin, M. L. J. Ashford, L. K. Modis,
 G. Brunori, D. C. Sévin, P. G. Fallon, S. T. Caldwell, E. R. S. Kunji, E. T. Chouchani, C. Frezza, A. T. DinkovaKostova, R. C. Hartley, M. P. Murphy and L. A. O'Neill, *Nature*, 2018, 556, 113–117.
- M. C. Runtsch, S. Angiari, A. Hooftman, R. Wadhwa, Y. Zhang, Y. Zheng, J. S. Spina, M. C. Ruzek, M. A.
 Argiriadi, A. F. McGettrick, R. S. Mendez, A. Zotta, C. G. Peace, A. Walsh, R. Chirillo, E. Hams, P. G. Fallon, R.
 Jayaraman, K. Dua, A. C. Brown, R. Y. Kim, J. C. Horvat, P. M. Hansbro, C. Wang and L. A. J. O'Neill, *Cell Metab.*, 2022, 34, 487-501.e8.
- 1022 235 C. V Maduka, A. V Makela, A. Tundo, E. Ural, K. B. Stivers, M. M. Kuhnert, M. Alhaj, E. Hoque Apu, N.
 1023 Ashammakhi, K. D. Hankenson, R. Narayan, J. H. Elisseeff and C. H. Contag, *Bioact. Mater.*, 2024, 40, 64–73.
- 1024 236 R. P. Allen, A. Bolandparvaz, J. A. Ma, V. A. Manickam and J. S. Lewis, *ACS Biomater. Sci. Eng.*, 2018, **4**, 900–1025 918.
- 1026 237 C. V Maduka, M. Alhaj, E. Ural, M. M. Kuhnert, O. M. Habeeb, A. L. Schilmiller, K. D. Hankenson, S. B. Goodman, R. Narayan and C. H. Contag, *ACS Biomater. Sci. Eng.*, 2023, **9**, 932–943.
- 1028 238 X. Shi, H. Zhou, J. Wei, W. Mo, Q. Li and X. Lv, Redox Biol., 2022, **58**, 102553.
- 1029 239 L. Tretter, A. Patocs and C. Chinopoulos, *Biochim. Biophys. Acta Bioenerg.*, 2016, **1857**, 1086–1101.

ess Article. Published on 27 juli 2024. Downloaded on 04-08-2024 11:14:49.	This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.
Open Acc	cc)) BY

1051

249

1030 1031 1032	240	L. Davenport Huyer, S. Mandla, Y. Wang, S. B. Campbell, B. Yee, C. Euler, B. F. Lai, A. D. Bannerman, D. S. Y. Lin, M. Montgomery, K. Nemr, T. Bender, S. Epelman, R. Mahadevan and M. Radisic, <i>Adv. Funct. Mater.</i> , 2021, 31 , 2003341.
1033 1034	241	L. Davenport Huyer, S. Pascual-Gil, Y. Wang, S. Mandla, B. Yee and M. Radisic, <i>Adv. Funct. Mater.</i> , , DOI:10.1002/adfm.201909331.
1035 1036	242	Y. Shou, S. B. Campbell, A. Lam, A. J. Lausch, J. P. Santerre, M. Radisic and L. Davenport Huyer, <i>ACS Appl. Polym. Mater.</i> , 2021, 3 , 1943–1955.
1037	243	V. Arias, A. Höglund, K. Odelius and AC. Albertsson, Biomacromolecules, 2014, 15, 391–402.
1038 1039	244	W. R. Lykins, D. A. Bernards, E. B. Schlesinger, K. Wisniewski and T. A. Desai, <i>Polymer (Guildf).</i> , 2022, 262 , 125473.
1040	245	A. I. Visan, G. Popescu-Pelin and G. Socol, <i>Polymers (Basel).</i> , , DOI:10.3390/polym13081272.
1041 1042	246	J. A. Jones, A. K. McNally, D. T. Chang, L. A. Qin, H. Meyerson, E. Colton, I. L. K. Kwon, T. Matsuda and J. M. Anderson, <i>J. Biomed. Mater. Res. Part A</i> , 2008, 84A , 158–166.
1043 1044 1045 1046 1047	247	J. Padmanabhan, K. Chen, D. Sivaraj, D. Henn, B. A. Kuehlmann, H. C. Kussie, E. T. Zhao, A. Kahn, C. A. Bonham, T. Dohi, T. C. Beck, A. A. Trotsyuk, Z. A. Stern-Buchbinder, P. A. Than, H. S. Hosseini, J. A. Barrera, N. J. Magbual, M. C. Leeolou, K. S. Fischer, S. S. Tigchelaar, J. Q. Lin, D. P. Perrault, M. R. Borrelli, S. H. Kwon, Z. N. Maan, J. C. Y. Dunn, R. Nazerali, M. Januszyk, L. Prantl and G. C. Gurtner, <i>Nat. Biomed. Eng.</i> , 2023, 7 , 1419–1436.
1048	248	S. MacLauchlan, E. A. Skokos, N. Meznarich, D. H. Zhu, S. Raoof, J. M. Shipley, R. M. Senior, P. Bornstein and

F. Ma, Y. Li, L. Jia, Y. Han, J. Cheng, H. Li, Y. Qi and J. Du, PLoS One, 2012, 7, e35144.

T. R. Kyriakides, J. Leukoc. Biol., 2009, 85, 617-626.

Data Availability Statement

No primary research results, software or code have been included and no new data were generated or analysed as part of this review.