

## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)Cite this: *Sustainable Energy Fuels*,  
2024, 8, 1944

Received 26th January 2024

Accepted 16th March 2024

DOI: 10.1039/d4se00146j

[rsc.li/sustainable-energy](https://rsc.li/sustainable-energy)Sequential proton coupled electron transfer events  
from a tetraruthenium polyoxometalate in  
photochemical water oxidation†Elena Rossin,<sup>a</sup> Marcella Bonchio,<sup>a</sup> Mirco Natali<sup>\*b</sup> and Andrea Sartorel<sup>\*a</sup>

The tetraruthenium polyoxometalate  $\{\text{Ru}^{\text{IV}}(\text{H}_2\text{O})_4(\mu\text{-OH})_2(\mu\text{-O})_4[\text{SiW}_{10}\text{O}_{36}]_2\}^{10-}$  ( $\text{Ru}_4\text{POM}$ ) shows multiple oxidative proton coupled electron transfer (PCET) events in a  $[\text{Ru}(\text{bpy})_3]^{2+}/\text{S}_2\text{O}_8^{2-}$  photochemical cycle for catalytic water oxidation, with electrons conveyed to the photogenerated  $[\text{Ru}(\text{bpy})_3]^{3+}$  oxidant and protons transferred to aqueous bases. As shown by laser flash photolysis, in aqueous phosphate buffer the consumption of the  $[\text{Ru}(\text{bpy})_3]^{3+}$  oxidant by  $\text{Ru}_4\text{POM}$  shows bi-exponential kinetics with a fast component and a slow component that feed the  $\text{Ru}_4\text{POM}$  catalyst with up to 6 oxidative equivalents through PCET in ca. 50 ms. The apparent rates of both the fast and slow components depend linearly on  $\text{HPO}_4^{2-}$  and on the pH of the aqueous medium, suggesting the involvement of the buffer base, of water and of  $\text{OH}^-$  in assisting removal of the protons from  $\text{Ru}_4\text{POM}$ . In particular, the beneficial role of  $\text{HPO}_4^{2-}$  is reflected in a proportional improvement in the oxygen evolution activity, reaching quantum efficiency approaching 14%, although an excessive increase of buffer concentration is detrimental to the  $[\text{Ru}(\text{bpy})_3]^{3+}$  stability and leads to the abatement of the  $\text{O}_2$  evolution.


## Introduction

Proton coupled electron transfer (PCET) is a pervasive process in many biological and artificial chemical transformations.<sup>1–4</sup> PCET events are often associated with photoinduced charge separation,<sup>5–10</sup> which is a primary step in chemical processes associated with the photosynthetic conversion of small molecules, while recently, its interest has broadened to synthetic organic chemistry.<sup>11–15</sup>

In the field of water oxidation, investigation of PCET was pioneered by T. J. Meyer, who recognized that for the  $[\text{Ru}^{\text{II}}(\text{H}_2\text{O})(\text{py})(\text{bpy})_2]^{2+}$  coordination complex (where py = pyridine; bpy = 2,2'-bipyridine) two stepwise oxidative PCET events occurring in a narrow potential window of 110 mV lead to the formation of a  $\text{Ru}^{\text{IV}}$ -oxo species;<sup>16</sup> these findings were pivotal in the design of the blue dimer  $[(\text{bpy})_2\text{Ru}^{\text{III}}(\text{H}_2\text{O})(\mu\text{-O})\text{Ru}^{\text{III}}(\text{H}_2\text{O})(\text{bpy})_2]^{4+}$  as the first molecular water oxidation catalyst.<sup>17</sup> The importance of PCET was then recognised in many ruthenium based catalytic manifolds,<sup>18–22</sup> including the case of the tetraruthenium polyoxometalate  $\{\text{Ru}^{\text{IV}}(\text{H}_2\text{O})_4(\mu\text{-OH})_2(\mu\text{-O})_4[\text{SiW}_{10}\text{O}_{36}]_2\}^{10-}$  ( $\text{Ru}_4\text{POM}$ ) investigated in this work (Scheme 1).  $\text{Ru}_4\text{POM}$  is the first structurally characterized polyoxometalate based water

oxidation catalyst,<sup>23,24</sup> and has been extensively investigated in electrochemical,<sup>25,26</sup> photochemical<sup>27,28</sup> and photo-electrochemical systems;<sup>29–32</sup> its tetraruthenium active core  $[\text{Ru}^{\text{IV}}(\text{H}_2\text{O})_4(\mu\text{-OH})_2(\mu\text{-O})_4]^{6+}$  can indeed undergo stepwise oxidation processes associated with the formation of high-valent intermediates characterised spectroscopically or with computational tools, up to the formation of Ru-oxo moieties active towards oxygen evolution at low overpotential.

Despite ruthenium catalysts being reported to show excellent performance in oxygenic photosynthetic systems,<sup>18,33–35</sup> the

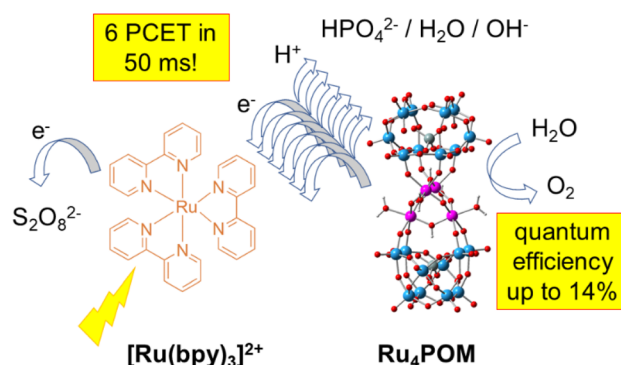

**Scheme 1** Multiple and sequential proton coupled electron transfer events from a tetraruthenium polyoxometalate  $\text{Ru}_4\text{POM}$  to photo-generated  $[\text{Ru}(\text{bpy})_3]^{3+}$  investigated in this work through laser flash photolysis, with  $\text{HPO}_4^{2-}$ ,  $\text{H}_2\text{O}$  and  $\text{OH}^-$  being responsible for proton transfer.

<sup>a</sup>Department of Chemical Sciences, University of Padova, Via Marzolo 1, 35131 Padova, Italy. E-mail: [Andrea.sartorel@unipd.it](mailto:Andrea.sartorel@unipd.it)

<sup>b</sup>Department of Chemical Pharmaceutical and Agricultural Sciences (DOCPAS), University of Ferrara, Ferrara, Italy. E-mail: [Mirco.natali@unife.it](mailto:Mirco.natali@unife.it)

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4se00146j>

managing of the necessary PCET events under photochemical conditions has been poorly investigated. Moreover, most of the PCET studies in photosynthetic systems for water oxidation refer to a single event,<sup>33</sup> and thus represent only the primary step in the water oxidation process.

In this study, we report multiple, sequential oxidative PCET events from Ru<sub>4</sub>POM to a photogenerated [Ru(bpy)<sub>3</sub>]<sup>3+</sup> oxidant (electron acceptor) highlighting the role of bases as the proton acceptors (Scheme 1). We will show by laser flash photolysis studies that the nature and concentration of the buffer impact the dynamics and the number of oxidation processes at the Ru<sub>4</sub>POM catalyst, showing a consistent effect in the O<sub>2</sub> evolving rate.

## Results and discussion

### Primary electron transfer from Ru<sub>4</sub>POM to [Ru(bpy)<sub>3</sub>]<sup>3+</sup>

In the laser flash photolysis set-up, [Ru(bpy)<sub>3</sub>]<sup>3+</sup> is photo-generated in a few ns upon laser excitation ( $\lambda_{\text{exc}} = 355$  nm) of a solution containing the [Ru(bpy)<sub>3</sub>]<sup>2+</sup> sensitizer and the S<sub>2</sub>O<sub>8</sub><sup>2-</sup> sacrificial acceptor (a quantum yield of 2 is reported for Ru(III) formation, since two equivalents of Ru(III) are generated upon one photon absorption according to the reaction steps in Scheme S1 in ESI†). Formation of Ru(III) is confirmed by the decrease of the absorbance at 450 nm (usually referred to as “bleach”, Fig. 1).

In the presence of Ru<sub>4</sub>POM, the Ru(II) initial absorption is restored in a few  $\mu$ s (“bleach recovery”, Fig. 1), indicating consumption of the [Ru(bpy)<sub>3</sub>]<sup>3+</sup> oxidant by Ru<sub>4</sub>POM, thus leading to the formation of the singly oxidized form of the Ru<sub>4</sub>POM catalyst, Ru<sub>4</sub>POM<sup>ox</sup>.†

Under pseudo first order conditions with [Ru<sub>4</sub>POM]  $\gg$  [[Ru(bpy)<sub>3</sub>]<sup>3+</sup>], fitting of the bleach recovery traces leads to the determination of the bimolecular rate constant  $k_I$  for the primary oxidative process in Ru<sub>4</sub>POM (eqn (1)), involving oxidation of one Ru<sup>IV</sup>-OH<sub>2</sub> moiety into Ru<sup>V</sup>-OH.



In order to map the possible involvement of a PCET event in this primary step, we performed the laser flash photolysis investigation in aqueous solutions at different pH values (in the range 2–7, conditions associated with the stability of Ru<sub>4</sub>POM in aqueous solution) employing different buffer and buffer concentrations. In Fig. 1, traces correspond to phosphate buffer at pH 7, while traces under other reaction conditions are reported in ESI (Fig. S1–S4).†

The main outcome of this analysis is that the primary oxidation of Ru<sub>4</sub>POM by [Ru(bpy)<sub>3</sub>]<sup>3+</sup> occurs under diffusion

† In all the experiments, 0.1 M Na<sub>2</sub>SO<sub>4</sub> was employed to guarantee a sufficient ionic strength of the medium ( $I = 0.3$  M), thus mitigating: (a) formation of [Ru(bpy)<sub>3</sub>]<sup>2+</sup>·Ru<sub>4</sub>POM ion pairs, where fast static quenching of the [Ru(bpy)<sub>3</sub>]<sup>2+</sup> photosensitizer hampers the occurrence of the envisaged photosynthetic cycle,<sup>27</sup> and (b) ET rate constant variability associated with the change of the ionic strength due to the change of buffer concentrations; the rate constant for a diffusion based ET event between charged reactants (as in the present case) is sensitive to the ionic strength according to the Debye–Eigen theory.<sup>49</sup>



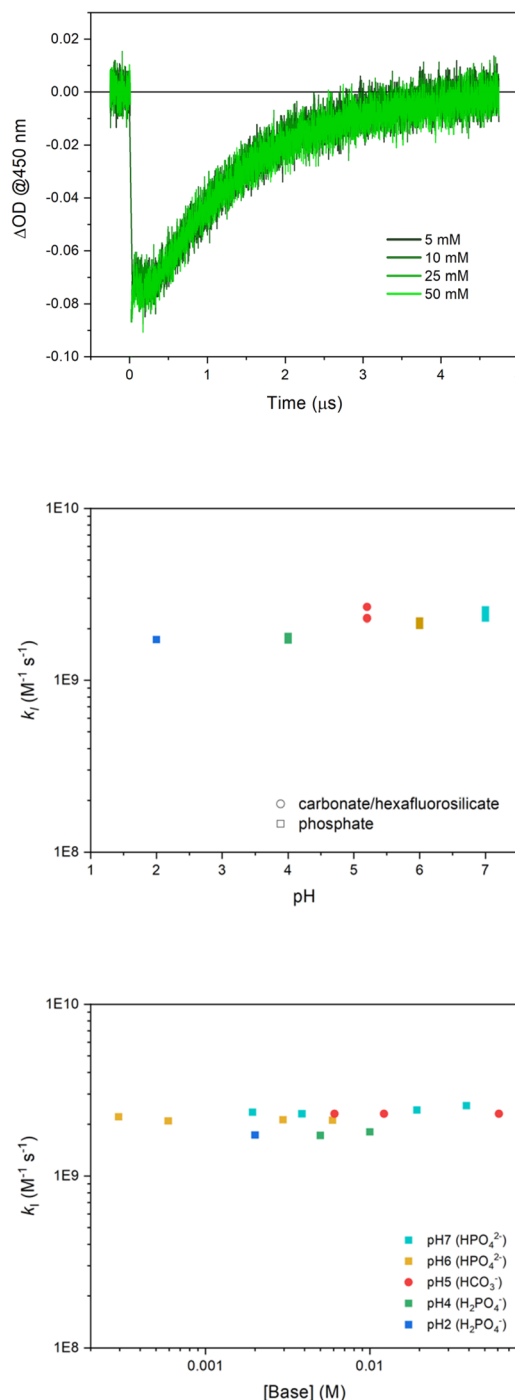


Fig. 1 (Top panel) Kinetic traces at 450 nm obtained by laser flash photolysis of 50  $\mu\text{M}$  Ru(bpy)<sub>3</sub>Cl<sub>2</sub>, 5 mM Na<sub>2</sub>S<sub>2</sub>O<sub>8</sub>, 30  $\mu\text{M}$  Na<sub>10</sub>Ru<sub>4</sub>POM, 0.1 M Na<sub>2</sub>SO<sub>4</sub> in 5–50 mM phosphate buffer at pH 7.0. (Medium panel) Bimolecular rate constant  $k_I$  (in logarithmic scale) for the primary oxidation of Ru<sub>4</sub>POM by [Ru(bpy)<sub>3</sub>]<sup>3+</sup> vs. pH (the different data at a specific pH refer to the different concentrations of the buffer employed). (Bottom panel)  $k_I$  (in logarithmic scale) vs. buffer base concentration for all experimental conditions tested (the different colours refer to the conditions employed, with the base specified in brackets in the legend panel).

control under all the conditions explored ( $k_I$  in the range  $1.7 \div 2.5 \times 10^9 \text{ M}^{-1} \text{s}^{-1}$ ).<sup>27</sup> The classical model for bimolecular ET reactions foresees the formation of the {[Ru(bpy)<sub>3</sub>]<sup>3+</sup>·Ru<sub>4</sub>POM}

encounter complex, eqn (2), followed by ET to form the successor complex  $\{[\text{Ru}(\text{bpy})_3]^{2+} \cdot \text{Ru}_4\text{POM}^{\text{ox}}\}$ , eqn (3), and product diffusion, eqn (4); assuming a steady state condition for the encounter and successor complexes the equation of the rate constant  $k_I$  can be expressed by eqn (5).<sup>36</sup>





$$k_I = \frac{k_1}{1 + (1 + k_{-2}/k_3) \times k_{-1}/k_2} \quad (5)$$

A diffusion limited  $k_I$  is expected when both  $k_3 \gg k_{-2}$  and  $k_2 \gg k_{-1}$ , in which case  $k_I \approx k_1$ ; this occurs under all the conditions explored for the process in eqn (1). This is beneficial towards the accumulation of the first oxidation equivalent in  $\text{Ru}_4\text{POM}^{\text{ox}}$  (*i.e.* backward processes do not significantly compete with forward processes in eqn (2)–(4)), but limits a mechanistic comprehension of the  $\text{Ru}_4\text{POM}$  to  $\text{Ru}_4\text{POM}^{\text{ox}}$  conversion, according to the expected PCET event from electrochemistry data.<sup>37</sup>

We then focused our analysis on multiple accumulation of oxidation equivalents in  $\text{Ru}_4\text{POM}$  by photogenerated  $[\text{Ru}(\text{bpy})_3]^{3+}$ .

### Multiple electron transfer events from $\text{Ru}_4\text{POM}$ to $[\text{Ru}(\text{bpy})_3]^{3+}$ : effect of pH, buffer, and buffer concentration

The fast accumulation of oxidation equivalents in  $\text{Ru}_4\text{POM}$  by photogenerated  $[\text{Ru}(\text{bpy})_3]^{3+}$  can be investigated by performing flash photolysis experiments using a low concentration of  $\text{Ru}_4\text{POM}$  to guarantee  $[\text{Ru}_4\text{POM}] \ll [[\text{Ru}(\text{bpy})_3]^{3+}]$  conditions.<sup>27</sup> With this setup, the amount of bleach recovery is associated with the number  $n$  of ET events from  $\text{Ru}_4\text{POM}$  to  $[\text{Ru}(\text{bpy})_3]^{3+}$  occurring in the timeframe of the experiment (50 ms), and generating a multiply oxidized form of the catalyst (eqn (6)), while the single steps can be represented as in eqn (7).



Experiments aimed at tracing multiple electron transfer events were conducted under aqueous conditions at different pH, buffer, and buffer concentrations. A representative example is shown in Fig. 2 (pH 7, 5–100 mM phosphate buffer), see ESI† for other traces (Fig. S5–S7†). The initial concentration of photochemically generated  $[\text{Ru}(\text{bpy})_3]^{3+}$  in Fig. 2 (top panel) is *ca.*  $2 \times 10^{-5}$  M and is obtained from the  $\Delta(\text{OD})^{450}$  abatement;<sup>§</sup>

§ The photogenerated concentration of  $[\text{Ru}(\text{bpy})_3]^{3+}$  is calculated from  $\Delta\epsilon^{450}(\text{Ru}(\text{II})/\text{Ru}(\text{III})) = 1.3 \times 10^4 \text{ M}^{-1} \text{ cm}^{-1}$  and the appropriate correction for the ratio between the volume of solution probed by the analysing beam and that excited by the laser pulse (1.35, as obtained from saturation techniques). As a result, a  $\Delta(\text{OD})$  of 0.1 corresponds to a concentration of photogenerated  $[\text{Ru}(\text{bpy})_3]^{3+}$  of  $1.04 \times 10^{-5}$  M.



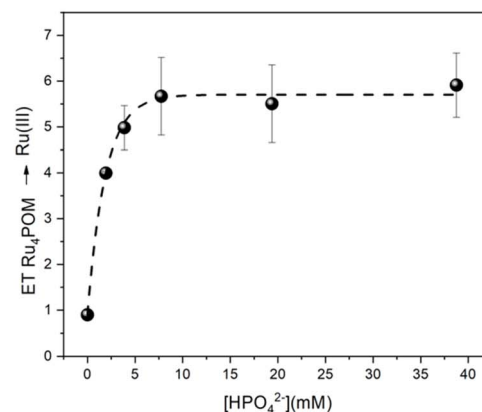


Fig. 2 (Top panel) Kinetic traces at 450 nm obtained by laser flash photolysis of 100  $\mu\text{M}$   $\text{Ru}(\text{bpy})_3\text{Cl}_2$ , 5 mM  $\text{Na}_2\text{S}_2\text{O}_8$ , 2.5  $\mu\text{M}$   $\text{Na}_{10}\text{Ru}_4\text{POM}$ , 0.1 M  $\text{Na}_2\text{SO}_4$  in unbuffered water and in 5–100 mM phosphate buffer at pH 7.0. The solid lines indicate the biexponential fittings of the traces (monoexponential fitting in the trace in water). (Bottom panel) Plot of the number of  $\text{Ru}_4\text{POM} \rightarrow [\text{Ru}(\text{bpy})_3]^{3+}$  ET events in 50 ms vs. the concentration of  $\text{HPO}_4^{2-}$  (base of the buffer). The number of ET events is estimated from the experimental recovery of the bleach in the kinetic traces in the top panel. The error bars are given as semi-dispersion of two separate experiments.

considering the concentration of 2.5  $\mu\text{M}$  of  $\text{Ru}_4\text{POM}$  employed in the experiment, the traces indicate that the amount of  $[\text{Ru}(\text{bpy})_3]^{3+}$  being reduced by  $\text{Ru}_4\text{POM}$  actually exceeds the amount of  $\text{Ru}_4\text{POM}$  and shows a dependence on the buffer concentration. The role of  $\text{Ru}_4\text{POM}$  in the reactivity of  $[\text{Ru}(\text{bpy})_3]^{3+}$  was confirmed by conducting experiments by varying the concentration of  $\text{Ru}_4\text{POM}$  (in the range 0.5–2.5  $\mu\text{M}$ ) and keeping the buffer concentration constant at 100 mM: the amount of  $\Delta(\text{OD})$  recovery of  $[\text{Ru}(\text{bpy})_3]^{3+}$  depends linearly on  $\text{Ru}_4\text{POM}$  concentration (Fig. S8 in ESI† and further discussion).

These results speak in favour of the occurrence of multiple PCET events from  $\text{Ru}_4\text{POM}$ , with the  $\text{HPO}_4^{2-}$  base of the buffer being responsible for the transfer of the protons, while electrons are conveyed to  $[\text{Ru}(\text{bpy})_3]^{3+}$ . The number of ET events increases up to a  $\text{HPO}_4^{2-}$  base concentration of *ca.* 15 mM, above which a plateau value of *ca.* 6 events is reached (Fig. 2, bottom panel). This concentration threshold is likely due to the availability of the

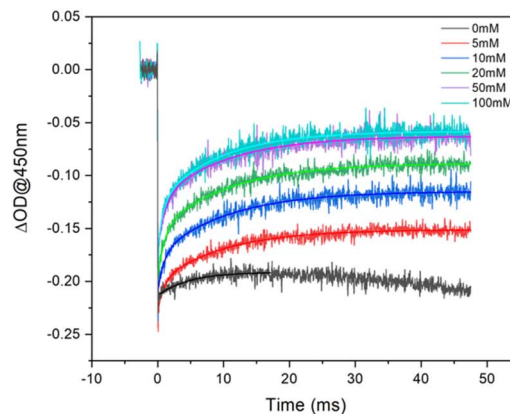

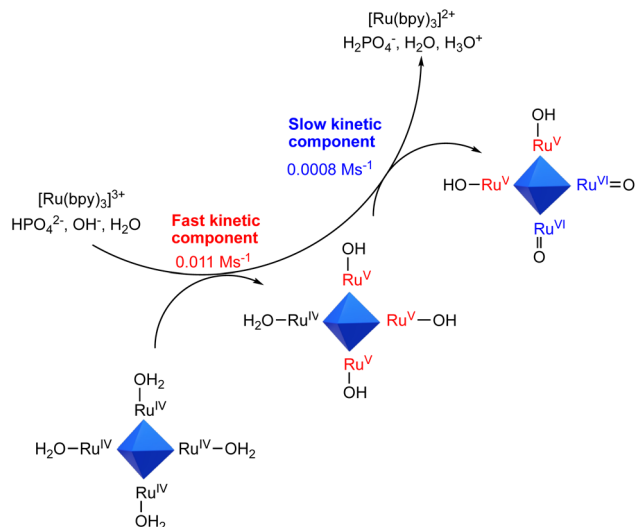

**Scheme 2** Schematic representation of the accumulation of oxidation equivalents on Ru<sub>4</sub>POM through sequential PCET involving [Ru(bpy)<sub>3</sub>]<sup>3+</sup> and aqueous bases within two kinetic regimes.

HPO<sub>4</sub><sup>2-</sup> base in proximity of the Ru<sub>4</sub>POM site reacting through PCET. Indeed, in the case of Ru<sub>4</sub>POM, accumulation of 6 oxidizing equivalents is associated with the generation of Ru<sup>VI</sup>oxo states through Ru<sup>IV</sup>(H<sub>2</sub>O)/Ru<sup>V</sup>(OH)/Ru<sup>VI</sup>(O) manifolds, subjected to a water nucleophilic attack as the first step finally releasing dioxygen in the catalytic cycle (Scheme 2).<sup>38</sup>

In order to extract kinetic parameters from the experimental traces in Fig. 2 we focused on the profile of consumption of [Ru(bpy)<sub>3</sub>]<sup>3+</sup> and used bi-exponential functions to describe the recovery of the Δ(OD) along the experiments, (eqn (8)):<sup>¶</sup>

$$\Delta(\text{OD}) = -A_F \times \exp(-t/\tau_F) - A_S \times \exp(-t/\tau_S) + \Delta(\text{OD})_{@50\text{ms}} \quad (8)$$

where  $\tau_F$  and  $\tau_S$  indicate a fast and a slow time constant, respectively,  $A_F$  and  $A_S$  indicate the amplitudes of the two components in the Δ(OD) recovery (Table 1), while Δ(OD)<sub>@50ms</sub> is the residual Δ(OD) value after 50 ms.

First, it is interesting to note that the relative amplitude contributions of the fast and slow components to the reactivity of [Ru(bpy)<sub>3</sub>]<sup>3+</sup> depend on the concentration of the buffer base (Fig. 3 top panel). The relative contributions of the fast and slow components – calculated as  $A_F \times 100/(A_F + A_S)$  and  $A_S \times 100/(A_F + A_S)$ , respectively – at low HPO<sub>4</sub><sup>2-</sup> concentrations are indeed 33% and 67%, respectively, while at high HPO<sub>4</sub><sup>2-</sup> concentrations the relative contributions reach plateau values of 45% and 55% for the fast and slow components, respectively.

<sup>¶</sup> In this case, a biexponential function was necessary to provide a suitable fitting of the experimental data. The use of a biexponential function to fit the traces where six sequential oxidation processes are postulated can be explained considering the similar reaction rates of the Ru<sub>4</sub>POM oxidized intermediates with [Ru(bpy)<sub>3</sub>]<sup>3+</sup>. This is indeed not unexpected taking into account the close spacing in potential associated with the oxidation of Ru<sub>4</sub>POM according to electrochemical studies.<sup>37</sup> The use of multiexponential functions is often exploited in the case of electron transfer involving metal oxide particles, due to the presence of surface sites with different reactivity.<sup>39</sup>

From the fitting parameters we then derived two apparent rates for the reactivity of [Ru(bpy)<sub>3</sub>]<sup>3+</sup> with Ru<sub>4</sub>POM due to the fast and slow components (eqn (9) and (10); the  $1.04 \times 10^{-4}$  factor converts the Δ(OD) units of  $A_F$  and  $A_S$  into the corresponding concentration of [Ru(bpy)<sub>3</sub>]<sup>3+</sup>):<sup>||</sup>

$$\text{App. Rate}_{\text{Fast}} (\text{M s}^{-1}) = A_F/\tau_F \times 1.04 \times 10^{-4} \quad (9)$$

$$\text{App. Rate}_{\text{Slow}} (\text{M s}^{-1}) = A_S/\tau_S \times 1.04 \times 10^{-4} \quad (10)$$

As shown in Fig. 3 (bottom panel and inset), the apparent rates determined above depend linearly on the concentration of the HPO<sub>4</sub><sup>2-</sup> base of the phosphate buffer (the log-log plot analysis supports a first order in [HPO<sub>4</sub><sup>2-</sup>] in both apparent rates, see ESI Fig. S10†).

$$\text{App. Rate}_{\text{Fast}} (\text{M s}^{-1}) = 2.62 \times 10^{-3} + 2.04 \times 10^{-4} [\text{HPO}_4^{2-}] \quad (11)$$

$$\text{App. Rate}_{\text{Slow}} (\text{M s}^{-1}) = 5.45 \times 10^{-4} + 6.38 \times 10^{-6} [\text{HPO}_4^{2-}] \quad (12)$$

The linear dependence of the rates on [HPO<sub>4</sub><sup>2-</sup>] confirms the role of the base in assisting the removal of the protons from Ru<sub>4</sub>POM along its conversion to highly oxidized states through reactivity with [Ru(bpy)<sub>3</sub>]<sup>3+</sup> (both apparent rates are indeed linearly dependent on Ru<sub>4</sub>POM concentration, see Fig. S11†).

For both the fast and slow apparent rates, the non-null intercept in eqn (11) and (12) indicates that HPO<sub>4</sub><sup>2-</sup> is not the only base assisting the reactivity of [Ru(bpy)<sub>3</sub>]<sup>3+</sup> towards Ru<sub>4</sub>POM. When conducting the analysis at lower pH (100 mM phosphate buffer pH 6) a significant abatement of both components of apparent rates was observed,<sup>\*\*</sup> Table 1 and Fig. 3, medium and bottom panels. Registration and fitting of a trace in water in the absence of any buffer (in this case through a monoexponential fitting) lead to the obtainment of a single component of the apparent rate, which was significantly abated with respect to the values previously determined. These results indicate that both OH<sup>-</sup> and H<sub>2</sub>O are involved in the reactivity of [Ru(bpy)<sub>3</sub>]<sup>3+</sup> towards Ru<sub>4</sub>POM (Scheme 2).<sup>36,39††</sup> The possibility for a base to assist PCET events is associated with the libido rule<sup>40,41</sup> and with the strength of the base, expressed in terms of the pK<sub>a</sub> of the conjugate acid/base couples (in this case: pK<sub>a</sub> = 7.2 for H<sub>2</sub>PO<sub>4</sub><sup>-</sup>/HPO<sub>4</sub><sup>2-</sup>, pK<sub>a</sub> = 0 for H<sub>3</sub>O<sup>+</sup>/H<sub>2</sub>O, pK<sub>a</sub> = 14 for H<sub>2</sub>O/OH<sup>-</sup>). Although H<sub>2</sub>O is the least basic, the possibility of preorganisation of water channels at the

<sup>||</sup> An alternative analysis considers the determination of an average time constant  $\langle\tau\rangle = (A_F \times \tau_F + A_S \times \tau_S)/(A_F + A_S)$ , and the determination of average apparent rates as:  $\text{App. Rate}_{\text{Average}} (\text{M}^{-1} \text{s}^{-1}) = (A_F + A_S)/\langle\tau\rangle \times 1.04 \times 10^{-4}$ . This leads to a consistent dependence of the average App. Rate on [HPO<sub>4</sub><sup>2-</sup>], see ESI (Fig. S9 and Table S1).<sup>†</sup>

<sup>\*\*</sup> At pH 6 (phosphate buffer), investigation of other buffer concentrations leads to a marked abatement of [Ru(bpy)<sub>3</sub>]<sup>2+</sup> recovery, thus hampering the possibility of exploring further the system. Reasonable data and fittings were obtained only for the conditions reported in the main text.

<sup>††</sup> The consumption of [Ru(bpy)<sub>3</sub>]<sup>3+</sup> by Ru<sub>4</sub>POM in the absence of buffer base could also be consistent with a stepwise mechanism ET/PT, in which electron transfer precedes proton transfer.





**Table 1** Fitting parameters according to eqn (8) for the traces in Fig. 2, top and medium panels.  $A_F$  and  $A_S$  are the intensity of  $\Delta(\text{OD})$  recovery associated with the fast and slow components, respectively, and can be converted into the total concentration of consumed  $[\text{Ru}(\text{bpy})_3]^{3+}$  multiplying them by a  $1.04 \times 10^{-4}$  M factor, see footnote §

Different pH and phosphate buffer concentrations <sup>a</sup>				
pH ([buffer], mM)	$A_F$ ( $\tau_F$ , ms)	$A_S$ ( $\tau_S$ , ms)	App. Rate <sub>Fast</sub> $\times 10^3$ , M s <sup>-1</sup>	App. Rate <sub>Slow</sub> $\times 10^3$ , M s <sup>-1</sup>
7 (5)	0.025 $\pm$ 0.001 (0.85 $\pm$ 0.04)	0.051 $\pm$ 0.004 (9.7 $\pm$ 0.1)	3.12 $\pm$ 0.19	04.54 $\pm$ 0.04
7 (10)	0.034 $\pm$ 0.001 (0.99 $\pm$ 0.06)	0.060 $\pm$ 0.001 (10.7 $\pm$ 0.2)	3.56 $\pm$ 0.24	0.58 $\pm$ 0.01
7 (20)	0.045 $\pm$ 0.001 (1.05 $\pm$ 0.04)	0.063 $\pm$ 0.004 (10.7 $\pm$ 0.2)	4.43 $\pm$ 0.19	0.61 $\pm$ 0.04
7 (50)	0.051 $\pm$ 0.001 (0.92 $\pm$ 0.05)	0.062 $\pm$ 0.001 (10.1 $\pm$ 0.2)	5.75 $\pm$ 0.33	0.64 $\pm$ 0.02
7 (100)	0.060 $\pm$ 0.002 (0.57 $\pm$ 0.03)	0.069 $\pm$ 0.001 (8.9 $\pm$ 0.1)	10.87 $\pm$ 0.67	0.80 $\pm$ 0.02
6 (100)	0.036 $\pm$ 0.001 (2.15 $\pm$ 0.12)	0.035 $\pm$ 0.001 (11.6 $\pm$ 0.5)	1.73 $\pm$ 0.11	0.31 $\pm$ 0.01
Water	0.022 $\pm$ 0.001 (4.0 $\pm$ 0.1)	—	0.56 $\pm$ 0.02	—
Different concentrations of Ru <sub>4</sub> POM (Fig. S8) <sup>b</sup>				
[Ru <sub>4</sub> POM] $\mu\text{M}$	$A_F$ ( $\tau_F$ , ms)	$A_S$ ( $\tau_S$ , ms)	App. Rate <sub>Fast</sub> $\times 10^3$ , M s <sup>-1</sup>	App. Rate <sub>Slow</sub> $\times 10^3$ , M s <sup>-1</sup>
2.5	0.060 $\pm$ 0.002 (0.57 $\pm$ 0.02)	0.069 $\pm$ 0.001 (8.9 $\pm$ 0.1)	10.87 $\pm$ 0.67	0.80 $\pm$ 0.20
1	0.043 $\pm$ 0.001 (1.29 $\pm$ 0.05)	0.058 $\pm$ 0.001 (9.7 $\pm$ 0.2)	3.44 $\pm$ 0.13	0.62 $\pm$ 0.17
0.5	0.038 $\pm$ 0.002 (3.05 $\pm$ 0.16)	0.039 $\pm$ 0.002 (13.7 $\pm$ 0.6)	1.30 $\pm$ 0.10	0.30 $\pm$ 0.20

<sup>a</sup> 100  $\mu\text{M}$   $\text{Ru}(\text{bpy})_3\text{Cl}_2$ , 5 mM  $\text{Na}_2\text{S}_2\text{O}_8$ , 2.5  $\mu\text{M}$   $\text{Na}_{10}\text{Ru}_4\text{POM}$ , 0.1 M  $\text{Na}_2\text{SO}_4$  in 5–100 mM phosphate buffer at pH 7.0, 100 mM phosphate buffer pH 6.0 or water. <sup>b</sup> 100  $\mu\text{M}$   $\text{Ru}(\text{bpy})_3\text{Cl}_2$ , 5 mM  $\text{Na}_2\text{S}_2\text{O}_8$ , 0.5–2.5  $\mu\text{M}$   $\text{Na}_{10}\text{Ru}_4\text{POM}$ , 0.1 M  $\text{Na}_2\text{SO}_4$  in 100 mM phosphate buffer at pH 7.0. In all cases the photogenerated  $[\text{Ru}(\text{bpy})_3]^{3+}$  estimated from the initial  $\Delta(\text{OD})$  is *ca.* 20  $\mu\text{M}$ .

hydrophilic surface of polyoxometalates may favour its role in assisting the transfer of protons during oxidation of  $\text{Ru}_4\text{POM}$ .<sup>36</sup> Finally, superimposable kinetic traces and unchanged fitting parameters were obtained when registering the experiment in deuterated medium (Fig. S12 in ESI,<sup>†</sup> obtained by laser flash photolysis of 100  $\mu\text{M}$   $\text{Ru}(\text{bpy})_3\text{Cl}_2$ , 5 mM  $\text{Na}_2\text{S}_2\text{O}_8$ , 2.5  $\mu\text{M}$   $\text{Na}_{10}\text{Ru}_4\text{POM}$ , 0.1 M  $\text{Na}_2\text{SO}_4$  in 100 mM deuterated phosphate buffer at pD 7.0), indicating a negligible H/D isotopic effect in the multiple ET dynamics. In single PCET events, small H/D isotope effects are indicative of a low modification of the overlap integrals of the donor-acceptor states along the proton transfer coordinate, when replacing H with D.<sup>42</sup>

The whole mechanistic scenario is represented in Scheme 2, where  $[\text{Ru}(\text{bpy})_3]^{3+}$  feeds  $\text{Ru}_4\text{POM}$  with 6 oxidizing equivalents up to  $\text{Ru}^{\text{VI}}=\text{O}$  states, with the assistance of aqueous bases in two distinct kinetic regimes. We finally attempted to estimate rate constants for the stepwise PCET processes by employing a kinetic model that considers 6 consecutive bimolecular events involving  $[\text{Ru}(\text{bpy})_3]^{3+}$  and  $\text{Ru}_4\text{POM}$  (previous eqn (7)), each one associated with a bimolecular rate constant  $k_j$  ( $j = 1-6$ ). Under the optimal conditions investigated (100 mM phosphate buffer, pH 7, purple trace in Fig. 2 top panel), the fitting provides values in the range  $1.3 \times 10^8 \div 2 \times 10^9 \text{ M}^{-1} \text{ s}^{-1}$  for  $k_1-k_3$  (associated with the fast component of the reactivity of  $[\text{Ru}(\text{bpy})_3]^{3+}$  and with the generation of the primary oxidized intermediates of  $\text{Ru}_4\text{POM}$ ) and  $1.2 \times 10^7 \div 4.5 \times 10^7 \text{ M}^{-1} \text{ s}^{-1}$  for  $k_4-k_6$  (associated with the slow component of the reactivity of  $[\text{Ru}(\text{bpy})_3]^{3+}$  and with the generation of the highly oxidized intermediates of  $\text{Ru}_4\text{POM}$ ). The slowing down of the rate for reaching highly oxidized  $\text{Ru}_4\text{POM}$  intermediates is expected based on less

favorable thermodynamics, according to the higher potentials associated with such species.<sup>37,38†‡</sup>

### Impact of the PCET mechanism in light driven O<sub>2</sub> evolution

We finally investigated the implication of the PCET mechanism and the effect of the buffer concentration on the O<sub>2</sub> evolution of the system, by irradiating 15 mL of an aqueous buffered solution containing 0.1 M  $\text{Na}_2\text{SO}_4$ , 1 mM  $\text{Ru}(\text{bpy})_3\text{Cl}_2$ , 5 mM  $\text{Na}_2\text{S}_2\text{O}_8$  and 5  $\mu\text{M}$  of  $\text{Na}_{10}\text{Ru}_4\text{POM}$  with a blue LED ( $\lambda_{\text{em}} = 450 \text{ nm}$ , FWHM 10 nm). The O<sub>2</sub> evolution traces are reported in Fig. 4, and show an initial linear production of O<sub>2</sub>, before reaching a plateau after 1–2 h irradiation. The key performance indicators are collected in Table 2; in this case, we considered the maximum O<sub>2</sub> evolving rate,  $\text{Rate}(\text{O}_2)_{\text{MAX}}$ , as the most significant one to evaluate the efficiency of the system and the effect of the buffer concentration. The main outcome can be summarised as follows:

(i) The system shows O<sub>2</sub> evolution activity also in the absence of buffer, with a  $\text{Rate}(\text{O}_2)_{\text{MAX}}$  of  $6.56 \times 10^{-4} \mu\text{mol}(\text{O}_2) \text{ s}^{-1}$ ; upon addition of the phosphate buffer (5–10 mM), an increase in  $\text{Rate}(\text{O}_2)_{\text{MAX}}$  is observed up to  $1.61 \times 10^{-3} \mu\text{mol}(\text{O}_2) \text{ s}^{-1}$  (Fig. 4 bottom panel; for consistency with previous data, we reported the  $\text{HPO}_4^{2-}$  base concentration in the abscissa). In oxygen evolution, the effect of the buffer can be related to multiple factors, including the aid in generating oxidized intermediates of the catalyst (*vide supra*), assisting the water nucleophilic attack and the oxygen–oxygen bond formation,<sup>38</sup> managing the protons released in the water oxidation process.

†† The kinetic model considering 6 consecutive oxidative events was applied also for the other experimental traces in the Fig. 2 top panel, but in these cases it led to overfitting of the data, see details in ESI.<sup>†</sup>



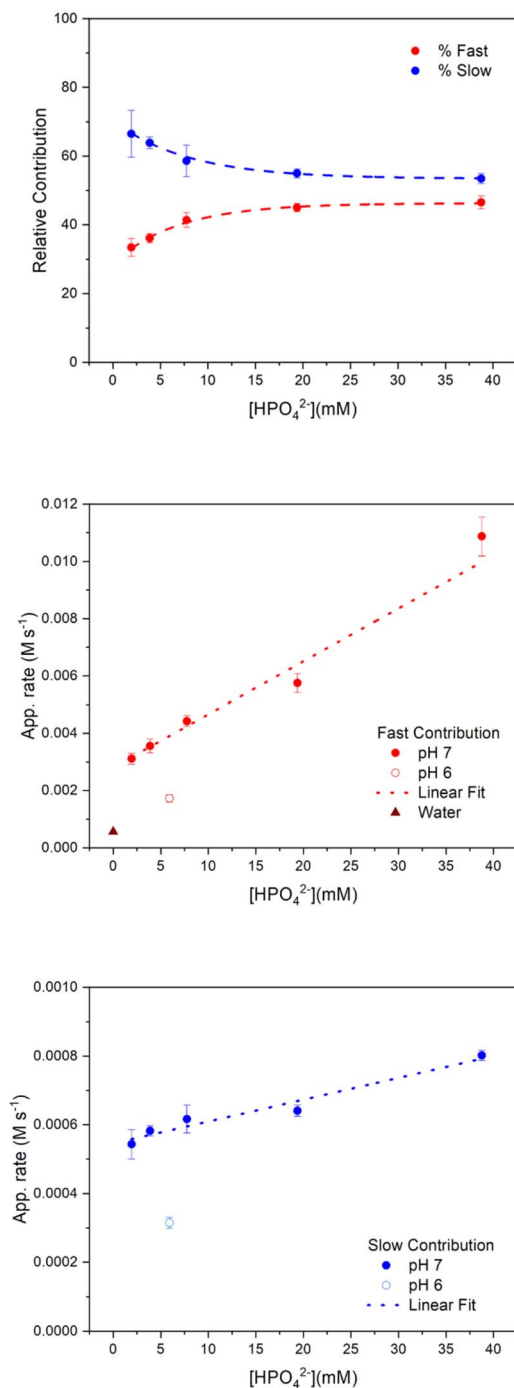


Fig. 3 (Top panel) Relative contribution of the two components to the recovery of the traces, calculated as  $A_F \times 100/(A_F + A_S)$  and  $A_S \times 100/(A_F + A_S)$ , respectively. (Medium panel) Plot of apparent rates for  $[\text{Ru}(\text{bpy})_3]^{3+}$  consumption vs. the concentration of base of the buffer for the fast contribution at different pH. (Bottom panel) Plot of apparent rates for  $[\text{Ru}(\text{bpy})_3]^{3+}$  consumption vs. the concentration of base of the buffer for the slow contribution at different pH.

(ii) A further increase of buffer concentration in the reaction conditions leads to a progressive abatement of  $\text{Rate}(\text{O}_2)_{\text{MAX}}$  (Fig. 4). This effect is ascribed to a rapid deactivation of the  $[\text{Ru}(\text{bpy})_3]^{2+}$  photosensitizer,<sup>43–45</sup> confirmed by UV-vis analysis of the reaction solution, which visibly turns from brilliant orange

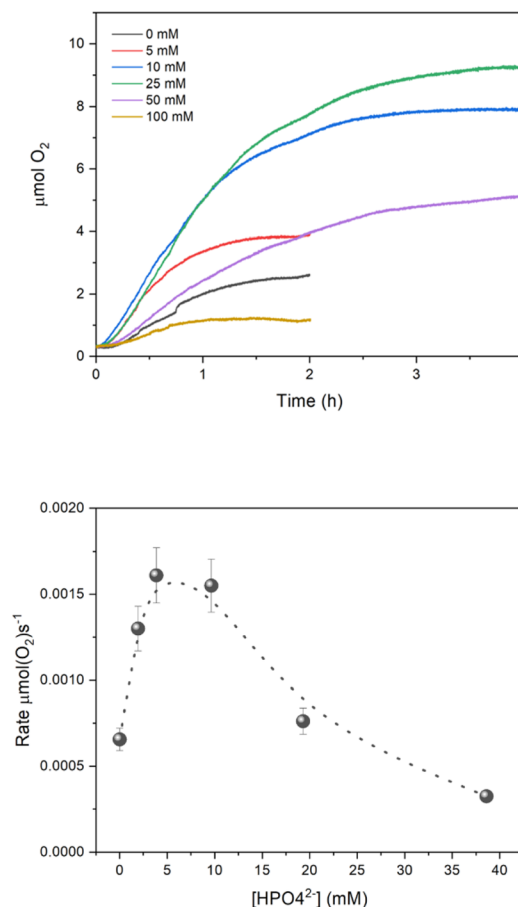


Fig. 4 (Top panel)  $\text{O}_2$  evolution kinetics (see Table 2 for conditions). (Bottom panel) Plot of  $\text{Rate}(\text{O}_2)_{\text{MAX}}$  vs. the concentration of  $\text{HPO}_4^{2-}$  buffer base. Error bars result from repetitive runs.

to brownish along the first minutes of irradiation (Fig. S13†). Recently, two decomposition pathways were elucidated for  $[\text{Ru}(\text{bpy})_3]^{2+}$  when combined with light and persulfate: a dark one, occurring at  $\text{pH} > 6$ , in which photogenerated  $[\text{Ru}(\text{bpy})_3]^{3+}$  reacts with  $\text{OH}^-$  to form  $\text{OH}^\bullet$  radicals which then attack the bpy ligands, and a light-induced one, starting from excitation of the  $[\text{Ru}(\text{bpy})_3]^{3+}$  oxidised state, promoting its reactivity with  $\text{S}_2\text{O}_8^{2-}$ .<sup>45</sup> Given the specific conditions employed in our study ( $\text{pH} 7$ , irradiation at  $450 \text{ nm}$  corresponding to the MLCT band of  $[\text{Ru}(\text{bpy})_3]^{2+}$ ) it is plausible that the dark decomposition pathway prevails, with  $\text{HPO}_4^{2-}$  being also involved in the radical reactivity.<sup>46</sup> Detrimental effects of high buffer concentration in water oxidation catalysis were previously documented under both light driven<sup>39</sup> and electrochemical conditions.<sup>47</sup>

(iii) Finally, under the optimized buffer conditions (10 mM), we explored the effect of light intensity on  $\text{O}_2$  generation. When reducing the photon flux from  $8.28 \times 10^{-8}$  to  $3.33 \times 10^{-8}$  and to  $0.87 \times 10^{-8} \text{ einstein s}^{-1}$ , a progressive decrease of  $\text{Rate}(\text{O}_2)_{\text{MAX}}$  was observed from  $1.61 \times 10^{-3}$  to  $1.16 \times 10^{-3}$  and to  $5.93 \times 10^{-4} \mu\text{mol}(\text{O}_2) \text{ s}^{-1}$ , indicative of light being a limiting reagent (Fig. S14†). Lowering the light intensity leads to an optimization of photon exploitation, as demonstrated by the quantum yield  $\phi(\text{O}_2)$  of the process reaching 6.8; this corresponds to a quantum efficiency for oxygen evolution of 13.6%, given that

**Table 2** Key performance parameters of the O<sub>2</sub> evolution kinetics. General conditions: 15 mL of an aqueous solution containing 0.1 M Na<sub>2</sub>SO<sub>4</sub>, 1 mM Ru(bpy)<sub>3</sub>Cl<sub>2</sub>, 5 mM Na<sub>2</sub>S<sub>2</sub>O<sub>8</sub> and 5 μM of Na<sub>10</sub>Ru<sub>4</sub>POM. Irradiation with a blue LED (λ<sub>em</sub> = 450 nm, FWHM 10 nm), photon flux = 8.28 × 10<sup>−8</sup> einstein s<sup>−1</sup>. The maximum rate is evaluated from a linear fitting of the initial part of the traces (between 10 and 30 minutes). Turnover frequency (TOF) and turnover numbers (TONs) are calculated with respect to Ru<sub>4</sub>POM

[Buffer] mM	Rate(O <sub>2</sub> ) <sub>MAX</sub> μmol(O <sub>2</sub> ) s <sup>−1</sup>	TOF × 10 <sup>2</sup> s <sup>−1</sup>	μmol(O <sub>2</sub> )	TON	QE%
—	6.56 × 10 <sup>−4</sup>	0.87 ± 0.1	2.8 ± 0.3	37 ± 3	1.6 ± 0.2
5	1.30 × 10 <sup>−3</sup>	1.73 ± 0.1	4.3 ± 0.4	57 ± 6	3.2 ± 0.2
10	1.61 × 10 <sup>−3</sup>	2.15 ± 0.2	8.0 ± 0.8	107 ± 9	3.8 ± 0.4
25	1.55 × 10 <sup>−3</sup>	2.07 ± 0.2	9.5 ± 0.9	127 ± 12	3.8 ± 0.4
50	7.62 × 10 <sup>−4</sup>	1.02 ± 0.1	5.1 ± 0.5	68 ± 6	1.8 ± 0.2
100	3.24 × 10 <sup>−4</sup>	0.43 ± 0.04	1.2 ± 0.1	16 ± 1	0.8 ± 0.1
10 <sup>a</sup>	1.16 × 10 <sup>−3</sup>	1.55 ± 0.1	8.4 ± 0.8	112 ± 11	6.8 ± 0.6
10 <sup>b</sup>	5.93 × 10 <sup>−4</sup>	0.79 ± 0.1	6.4 ± 0.6	85 ± 8	13.6 ± 1.2

<sup>a</sup> Photon flux = 3.33 × 10<sup>−8</sup> einstein s<sup>−1</sup>. <sup>b</sup> Photon flux = 0.87 × 10<sup>−8</sup> einstein s<sup>−1</sup>.

a theoretical maximum quantum yield  $\phi(\text{O}_2) = 0.50$  is expected with the [Ru(bpy)<sub>3</sub>]<sup>2+</sup>/S<sub>2</sub>O<sub>8</sub><sup>2−</sup> cycle, where the production of one oxygen molecule theoretically requires the absorption of two photons (see Scheme S1 in ESI†).<sup>48</sup> A value of 9% for quantum efficiency was previously reported in the literature under similar reaction conditions but with 420–520 nm irradiation.<sup>28</sup>

## Conclusions and perspectives

We investigated the accumulation of oxidizing equivalents on the Ru<sub>4</sub>POM water oxidation catalyst through PCET events in a [Ru(bpy)<sub>3</sub>]<sup>2+</sup>/S<sub>2</sub>O<sub>8</sub><sup>2−</sup> photochemical cycle. Laser flash photolysis experiments indicate the occurrence of 6 oxidative PCET events on Ru<sub>4</sub>POM in *ca.* 50 ms, leading to the generation of competent Ru<sup>VI</sup>-oxo intermediates. While electrons are conveyed from Ru<sub>4</sub>POM to the [Ru(bpy)<sub>3</sub>]<sup>3+</sup> oxidant, protons are transferred to aqueous bases. The flash photolysis traces show indeed two components of the rate of [Ru(bpy)<sub>3</sub>]<sup>3+</sup> reactivity, both linearly dependent on the HPO<sub>4</sub><sup>2−</sup> buffer base concentration; a contribution of H<sub>2</sub>O and OH<sup>−</sup> in managing protons was also highlighted. The effect of HPO<sub>4</sub><sup>2−</sup> buffer base was evident also in O<sub>2</sub> evolving kinetics, inducing a progressive increase of O<sub>2</sub> rate up to 5–10 mM, above which the system loses activity due to [Ru(bpy)<sub>3</sub>]<sup>2+</sup> photosensitizer fast decomposition. Under optimal buffer composition, managing light intensity led to reaching a quantum efficiency up to 13.6%.

This work highlights the importance of considering the molecular nature of PCET events under photochemical conditions, since this can significantly impact the efficiency of the overall process. The investigation of this aspect is expected to be general and broad, given the fact that PCET events are pervasive in many chemical transformations.

## Experimental part

### Instrumentation and procedures

Na<sub>10</sub>{Ru<sup>IV</sup>(H<sub>2</sub>O)<sub>4</sub>(μ-OH)<sub>2</sub>(μ-O)<sub>4</sub>[SiW<sub>10</sub>O<sub>36</sub>]<sub>2</sub>} (Na<sub>10</sub>Ru<sub>4</sub>POM) was synthesised as previously reported.<sup>29–31</sup>

Nanosecond transient absorption measurements were performed with a custom laser spectrometer consisting of

a Continuum Surelite II Nd:YAG laser (FWHM 6–8 ns) with an option to double (532 nm) or triple (355 nm) the frequency, an Applied Photo-physics xenon light source including a mod. 720 150 W lamp housing, a mod. 620 power-controlled lamp supply and a mod. 03-102 arc lamp pulser. Laser excitation was provided at 90° with respect to the white light probe beam. Light transmitted by the sample was focused onto the entrance slit of a 300 mm focal length Acton SpectraPro 2300i triple grating, flat field, double exit monochromator equipped with a photo-multiplier detector (Hamamatsu R3896) and a Princeton Instruments PIMAX II gated intensified CCD camera, using an RB Gen II intensifier, an ST133 controller and a PTG pulser. Signals from the photomultiplier (Hamamatsu R928) were processed by means of a Teledyne LeCroy 604Zi digital oscilloscope (400 MHz, 20 GS s<sup>−1</sup>).

Light driven catalytic tests for water oxidation were conducted in a home-made glass reactor, equipped with a TROX-ROB10 oxygen probe inserted in the headspace, and connected with a FirestingO2 fiber-optical oxygen meter for real time monitoring of evolved O<sub>2</sub>. 15 mL of aqueous buffer was introduced into the reactor, which was then closed and purged under a dark atmosphere with nitrogen for 20 minutes: after purging, the solution was allowed to equilibrate in the dark for 5 minutes and then illuminated with a series of six monochromatic LEDs emitting at 450 nm, photon flux = (8.28 ÷ 0.87) × 10<sup>−8</sup> einstein s<sup>−1</sup>. The irradiation power of the LEDs was measured with an AvaSpec-2048 Fiber Optic Spectrometer from Avantes.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

Financial support from Ministero dell'Università e della Ricerca (PRIN 2022 PROMETEO, 2022KPK8WM), by the European Union – Next Generation EU (PRIN2022 PNRR PHOTOCORE, P2022ZSPWF) and from Fondazione Cariparo (Project “SYNERGY”, Ricerca Scientifica di Eccellenza 2018) is greatly acknowledged. We thank the National Recovery and Resilience Plan (NRRP), Mission 4 Component 2 Investment 1.3 – Call for



tender No. 1561 of 11.10.2022 of MUR, funded by the European Union – NextGenerationEU, Project code PE000002 “Network 4 Energy Sustainable Transition – NEST”.

## Notes and references

- 1 R. G. Agarwal, S. C. Coste, B. D. Groff, A. M. Heuer, H. Noh, G. A. Parada, C. F. Wise, E. M. Nichols, J. J. Warren and J. M. Mayer, *Chem. Rev.*, 2022, **122**, 1–49.
- 2 R. Tyburski, T. Liu, S. D. Glover and L. Hammarström, *J. Am. Chem. Soc.*, 2021, **143**, 560–576.
- 3 G. A. Parada, Z. K. Goldsmith, S. Kolmar, B. P. Rimgard, B. Q. Mercado, L. Hammarström, S. Hammes-Schiffer and J. M. Mayer, *Science*, 2019, **475**, 471–475.
- 4 M. C. Kessinger, J. Xu, K. Cui, Q. Loague, A. V. Soudackov, S. Hammes-Schiffer and G. J. Meyer, *J. Am. Chem. Soc.*, 2024, **146**, 1742–1747.
- 5 M. Natali, A. Amati, S. Merchiori, B. Ventura and E. Iengo, *J. Phys. Chem. C*, 2020, **124**, 8514–8525.
- 6 M. Natali, A. Amati, N. Demitri and E. Iengo, *Chem.–Eur. J.*, 2021, **27**, 7872–7881.
- 7 E. Benazzi, J. Karlsson, Y. Ben M'Barek, P. Chabera, S. Blanchard, S. Alves, A. Proust, T. Pullerits, G. Izzet and E. A. Gibson, *Inorg. Chem. Front.*, 2021, **8**, 1610–1618.
- 8 M. Kuss-Petermann, M. Oraziotti, M. Neuburger, P. Hamm and O. S. Wenger, *J. Am. Chem. Soc.*, 2017, **139**, 5225–5232.
- 9 A. Pannwitz and O. S. Wenger, *Chem. Commun.*, 2019, **55**, 4004–4014.
- 10 A. Dey, N. Ghorai, A. Das and H. N. Ghosh, *J. Phys. Chem. B*, 2020, **124**, 11165–11174.
- 11 T. F. Markle, J. W. Darcy and J. M. Mayer, *Sci. Adv.*, 2018, **4**, eaat5776.
- 12 P. R. D. Murray, J. H. Cox, N. D. Chiappini, C. B. Roos, E. A. McLoughlin, B. G. Hejna, S. T. Nguyen, H. H. Ripberger, J. M. Ganley, E. Tsui, N. Y. Shin, B. Koronkiewicz, G. Qiu and R. R. Knowles, *Chem. Rev.*, 2022, **122**, 2017–2291.
- 13 P. Franceschi, E. Rossin, G. Goti, A. Scapano, A. Vega-Penaloza, M. Natali, D. Singh, A. Sartorel and L. D. Amico, *J. Org. Chem.*, 2023, **88**, 6454–6464.
- 14 T. Bortolato, G. Simionato, M. Vayer, C. Rosso, L. Paoloni, E. M. Benetti, A. Sartorel, D. Lebœuf and L. Dell'Amico, *J. Am. Chem. Soc.*, 2023, **145**, 1835–1846.
- 15 Y. Yang, G. A. Volpato, E. Rossin, N. Peruffo, F. Tumbarello, C. Nicoletti, R. Bonetto, L. Paoloni, P. Umari, E. Colusso, L. Dell'Amico, S. Berardi, E. Collini, S. Caramori, S. Agnoli and A. Sartorel, *ChemSusChem*, 2023, e202201980.
- 16 B. P. Sullivan, D. J. Salmon and T. J. Meyer, *Inorg. Chem.*, 1978, **17**, 3334–3341.
- 17 S. W. Gersten, G. J. Samuels and T. J. Meyer, *J. Am. Chem. Soc.*, 1982, **104**, 4029–4030.
- 18 M. Schulze, V. Kunz, P. D. Frischmann and F. Würthner, *Nat. Chem.*, 2016, **8**, 576–583.
- 19 M. A. Hoque, M. Gil-Sepulcre, A. de Aguirre, J. A. A. W. Elemans, D. Moonshiram, R. Matheu, Y. Shi, J. Benet-Buchholz, X. Sala, M. Malfois, E. Solano, J. Lim, A. Garzón-Manjón, C. Scheu, M. Lanza, F. Maseras, C. Gimbert-Suriñach and A. Llobet, *Nat. Chem.*, 2020, **12**, 1060–1066.
- 20 R. Matheu, P. Garrido-Barros, M. Gil-Sepulcre, M. Z. Ertem, X. Sala, C. Gimbert-Suriñach and A. Llobet, *Nat. Rev. Chem.*, 2019, **3**, 331–341.
- 21 L. Duan, F. Bozoglian, S. Mandal, B. Stewart, T. Privalov, A. Llobet and L. Sun, *Nat. Chem.*, 2012, **4**, 418–423.
- 22 R. Matheu, M. Z. Ertem, J. Benet-Buchholz, E. Coronado, V. S. Batista, X. Sala and A. Llobet, *J. Am. Chem. Soc.*, 2015, **137**, 10786–10795.
- 23 A. Sartorel, M. Carraro, G. Scorrano, R. De Zorzi, S. Geremia, N. D. McDaniel, S. Bernhard and M. Bonchio, *J. Am. Chem. Soc.*, 2008, **130**, 5006–5007.
- 24 Y. V. Geletii, B. Botar, P. Kögerler, D. A. Hillesheim, D. G. Musaev and C. L. Hill, *Angew. Chem., Int. Ed.*, 2008, **47**, 3896–3899.
- 25 F. M. Toma, A. Sartorel, M. Iurlo, M. Carraro, P. Parris, C. MacCato, S. Rapino, B. R. Gonzalez, H. Amenitsch, T. Da Ros, L. Casalis, A. Goldoni, M. Marcaccio, G. Scorrano, G. Scoles, F. Paolucci, M. Prato and M. Bonchio, *Nat. Chem.*, 2010, **2**, 826–831.
- 26 S. X. Guo, Y. Liu, C. Y. Lee, A. M. Bond, J. Zhang, Y. V. Geletii and C. L. Hill, *Energy Environ. Sci.*, 2013, **6**, 2654–2663.
- 27 M. Natali, M. Orlandi, S. Berardi, S. Campagna, M. Bonchio, A. Sartorel and F. Scandola, *Inorg. Chem.*, 2012, **51**, 7324–7331.
- 28 Y. V. Geletii, Z. Huang, Y. Hou, D. G. Musaev, T. Lian and C. L. Hill, *J. Am. Chem. Soc.*, 2009, **131**, 7522–7523.
- 29 G. A. Volpato, M. Marasi, T. Gobatto, F. Valentini, F. Sabuzi, V. Gagliardi, A. Bonetto, A. Marcomini, S. Berardi, V. Conte, M. Bonchio and S. Caramori, *Chem. Commun.*, 2020, **56**, 2248–2251.
- 30 T. Gobatto, F. Rigodanza, E. Benazzi, P. Costa, M. Garrido, A. Sartorel, M. Prato and M. Bonchio, *J. Am. Chem. Soc.*, 2022, **144**, 14021–14025.
- 31 M. Bonchio, Z. Syrgiannis, M. Burian, N. Marino, E. Pizzolato, K. Dirian, F. Rigodanza, G. A. Volpato, G. La Ganga, N. Demitri, S. Berardi, H. Amenitsch, D. M. Guldi, S. Caramori, C. A. Bignozzi, A. Sartorel and M. Prato, *Nat. Chem.*, 2019, **11**, 146–153.
- 32 J. Fielden, J. M. Sumliner, N. Han, Y. V. Geletii, X. Xiang, D. G. Musaev, T. Lian and C. L. Hill, *Chem. Sci.*, 2015, **6**, 5531–5543.
- 33 H. Song, A. Amati, A. Pannwitz, S. Bonnet and L. Hammarström, *J. Am. Chem. Soc.*, 2022, **144**, 19353–19364.
- 34 Y. Xu, L. Duan, L. Tong, B. Åkermarck and L. Sun, *Chem. Commun.*, 2010, **46**, 6506.
- 35 Y. Xu, A. Fischer, L. Duan, L. Tong, E. Gabrielsson, B. Åkermarck and L. Sun, *Angew. Chem., Int. Ed.*, 2010, **49**, 8934–8937.
- 36 F. Rigodanza, N. Marino, A. Bonetto, A. Marcomini, M. Bonchio, M. Natali and A. Sartorel, *ChemPhysChem*, 2021, **22**, 1208–1218.
- 37 Y. Liu, S. Guo, A. M. Bond, J. Zhang, Y. V. Geletii and C. L. Hill, *Inorg. Chem.*, 2013, **52**, 11986–11996.





- 38 S. Piccinin, A. Sartorel, G. Aquilanti, A. Goldoni, M. Bonchio and S. Fabris, *Proc. Natl. Acad. Sci. U. S. A.*, 2013, **110**, 4917–4922.
- 39 G. A. Volpato, A. Bonetto, A. Marcomini, P. Mialane, M. Bonchio, M. Natali and A. Sartorel, *Sustainable Energy Fuels*, 2018, **2**, 1951–1956.
- 40 W. P. Jencks, *J. Am. Chem. Soc.*, 1972, **94**, 4731–4732.
- 41 W. Jencks, *Chem. Rev.*, 1972, **72**, 705–718.
- 42 S. Hammes-Schiffer, *J. Am. Chem. Soc.*, 2015, **137**, 8860–8871.
- 43 P. K. Ghosh, B. S. Brunschwig, M. Chou, C. Creutz and N. Sutin, *J. Am. Chem. Soc.*, 1984, **106**, 4772–4783.
- 44 C. T. Lin, W. Böttcher, M. Chou, C. Creutz and N. Sutin, *J. Am. Chem. Soc.*, 1976, **98**, 6536–6544.
- 45 U. S. Akhtar, E. L. Tae, Y. S. Chun, I. C. Hwang and K. B. Yoon, *ACS Catal.*, 2016, **6**, 8361–8369.
- 46 J. Lee, U. Von Gunten and J. H. Kim, *Environ. Sci. Technol.*, 2020, **54**, 3064–3081.
- 47 D. Wang and J. T. Groves, *Proc. Natl. Acad. Sci. U. S. A.*, 2013, **110**, 15579–15584.
- 48 A. Volpe, C. Tubaro, M. Natali, A. Sartorel, G. W. Brudvig and M. Bonchio, *Inorg. Chem.*, 2019, **58**, 16537–16545.
- 49 C. Chiorboli, M. T. Indelli, M. A. R. Scandola and F. Scandola, *J. Phys. Chem.*, 1988, **92**, 156–163.

