

Materials Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: D. Kang, H. Heo, E. Jeong, H. Yang, D. Koh, C. W. Park and H. Kim, *Mater. Adv.*, 2026, DOI: 10.1039/D6MA00202A.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

ARTICLE

Hydrophobic Block-Structured PDMS/Pt-mesoporous Silica Catalysts for Sustainable Water-Hydrogen Isotope Exchange

Daeuk Kang,^{a,b} Huiryung Heo,^c Euna Jeong,^d Hee-Man Yang,^{a,b} Dong-Yeun Koh,^c Chan Woo Park,^{*b} Hyung-Ju Kim^{*a,b}Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Efficient separation of hydrogen isotopes is essential for sustainable hydrogen management and environmental protection in nuclear and other industrial systems. Conventional hydrogen isotope separation technologies, including cryogenic distillation, Girdler sulfide process and ammonia–hydrogen exchange, consume massive energy and involve corrosive or toxic reagents, leading to significant environmental and operational challenges. In contrast, the liquid phase catalytic exchange (LPCE) process, based on water–hydrogen gas isotope exchange, provides an efficient and energy-conserving alternative consistent with sustainable catalytic processes. In this study, a platinum decorated mesoporous silica-polydimethylsiloxane composite (Pt@SiO₂-PDMS) was developed and applied as a catalyst for LPCE process. Physico-chemical characterizations verified the decoration of Pt into the mesoporous silica without destruction of mesoporous structure. The Pt@SiO₂ particles were homogeneously distributed in the PDMS matrix and the resulting composite maintained an intrinsic hydrophobic surface with a water contact angle above 108°. The catalyst composite exhibited effective hydrogen isotope exchange performance up to column efficiency of 67.7% at 80 °C when Pt@SiO₂-PDMS randomly packed with Dixon rings in a volume ratio of 2:1 in the LPCE process. Furthermore, stable operation was maintained continuously for 14 days at 80 °C, demonstrating the durability of catalyst composite and application on actual process conditions. The selective hydrogen isotope exchange between liquid water and hydrogen gas with Pt@SiO₂-PDMS catalyst is attributed to the effective porous structure of SiO₂, Pt loading of Pt@SiO₂ and hydrophobic nature of the PDMS matrix.

Introduction

Hydrogen isotope separation has gained increasing attention due to its growing demand ranging from nuclear technology to advanced manufacturing of electronic devices.^{1,2} The expanded use of deuterium (D) in industrial processes and the continuous generation of tritium (T) in nuclear systems have further highlighted the need for reliable and efficient isotope separation.¹ In nuclear power systems, heavy-water reactors utilize deuterium oxide (D₂O) as moderator and coolant, providing outstanding neutron economy and efficient moderation.³ Beyond nuclear applications, D₂O, as a valuable resource, is also utilized in advanced industrial and electronic fields such as manufacturing of organic light-emitting diode.⁴ On the other hand, T, radioactive hydrogen isotope, is

produced inside of nuclear reactors through neutron capture and nuclear transmutation reactions and the quantity is significant in heavy water reactors and fusion research facilities.⁵ Since T exhibits physicochemical properties nearly identical to protium (H) and D, separation of hydrogen isotope is extremely hard to be achieved via conventional chemical separation processes.⁶ Once T is released into the environment, it is easily spread out to the atmosphere, hydrosphere and biosphere, thereby causes harmful effect on living organisms. Thus, proper long-term management plan including separation technology for hydrogen isotope is required.⁷ Furthermore, the recent release of T contaminated water from the Fukushima Daiichi nuclear power plant has intensified the need for development of efficient and cost-effective hydrogen isotope separation technologies.⁸

Various hydrogen isotope separation techniques have been developed, including water distillation,⁹ cryogenic distillation¹⁰ and chemical isotope exchange.¹¹ Water distillation, which relies on the vapor pressure difference between water isotopologues, has a low separation factor ($\alpha_{H/T} = 1.04\text{--}1.07$), leading to high energy consumption ($\sim 80 \text{ GJ kg}^{-1} \text{ D}_2\text{O}$).^{12,13} Cryogenic distillation, which separates hydrogen gas isotopologues at liquefaction temperatures, is limited by a low separation factor ($\alpha_{D/H} \approx 1.5$ at $-249 \text{ }^\circ\text{C}$),¹⁴ high operational costs ($\sim 22 \text{ GJ kg}^{-1} \text{ D}_2\text{O}$),¹⁵ and difficulties in system maintenance.¹⁶ On the other hand, chemical isotope exchange driven by equilibrium reactions between hydrogen gas and hydrogen-

^a Nuclear Science and Technology, University of Science and Technology, 217 Gajeong-ro, Yuseong-gu, Daejeon 34113, Republic of Korea

^b Nuclear Facility Cleanup Technology Division, Korea Atomic Energy Research Institute, 989-111 Daedeok-daero, Yuseong-gu, Daejeon 34057, Republic of Korea. E-mail: hyungjukim@kaeri.re.kr, chanwoo@kaeri.re.kr

^c Department of Chemical and Biomolecular Engineering, Korea Advanced Institute of Science and Technology, 291, Daehak-ro, Yuseong-gu, Daejeon, 34141, Republic of Korea

^d Radioactive Waste Technology Team, Korea Research Institute of Decommissioning, 569, Haemaji-ro, Jangan-eup, Gijang-gun, Busan, 46035, Republic of Korea

^e Department of Chemical and Biomolecular Engineering, Korea Advanced Institute of Science and Technology, 291, Daehak-ro, Yuseong-gu, Daejeon, 34141, Republic of Korea



containing molecules (such as H₂S, NH₃ or H₂O), are considered commercially valuable due to their high separation factors and the feasibility of operation under technically viable temperature conditions.¹⁷ For example, chemical isotope exchange process such as the Girdler sulfide and ammonia–hydrogen were primarily developed and commercialized for D enrichment in D₂O production.¹⁸ Although these techniques possess high isotope separation efficiency, they involve the use of toxic or corrosive reagents and require a large amount of energy (~30 GJ kg⁻¹ D₂O for the Girdler sulfide process and ~11 GJ kg⁻¹ D₂O for ammonia–hydrogen exchange),¹⁵ and exhibit a relatively low separation factor of approximately 2,¹⁹ which limit their environmental and economic sustainability.²⁰ Meanwhile, the chemical isotope exchange between hydrogen gas and liquid water via the liquid phase catalytic exchange (LPCE) process is considered the most promising approach for environmentally benign isotope separation and detritiation.¹⁴ This process allows T to be either concentrated in or extracted from water, depending on the equilibrium reaction conditions. Also, LPCE offers advantages such as low energy consumption, as it can be operated under ambient pressure and relatively mild temperature ranging from 60 to 80 °C without extreme energy,²¹ a high separation factor ($\alpha_{H/D} \approx 5$ at 70 °C), and environmental sustainability.^{22,23} In South Korea, the Wolsong nuclear power plant operates a T removal facility, where the LPCE process is industrially applied as the primary step to extract T from tritiated D₂O, followed by cryogenic distillation to further enrich tritium as T₂ (Fig. S1 of Supplementary Information).¹¹

The performance of the LPCE process is highly dependent on the catalyst that facilitates isotope exchange reaction between hydrogen isotopes. The activity and stability of catalyst are critical factors that determine reaction efficiency and size of column directly correlated to the cost-effectiveness,²⁴ because functional and structural property of catalyst surface critically influences catalytic performance.^{25–27} Currently, platinum (Pt)-based catalysts are the most widely used in LPCE due to their high reaction rate, but their catalytic activity may gradually decline over long-term operation due to surface poisoning and structural deformation.²⁸ Even worse, the active sites can be blocked due to the penetration of liquid water into the catalyst. Since the LPCE process is a multi-phase reaction involving liquid water, water vapor and hydrogen gas, excessive exposure and physical as well as chemical adsorption of liquid water and water vapor on the catalyst surface block active sites, thereby reducing reaction efficiency.²⁹ Therefore, catalysts for LPCE should possess hydrophobicity with a large active surface area to enhance catalytic activity, while facilitating the diffusion of water vapor. To address this issue, design of catalyst relies on the combination of porous and hydrophobic framework have been studied. Metal-organic frameworks (MOFs),³⁰ zeolites,³¹ carbon-based materials³² and mesoporous silica³³ serve as catalyst supports, and they provide a large number of active sites due to their high specific surface area,²¹ where controlled nanostructure and dispersion can significantly influence catalytic behavior.³⁴ However, MOFs reported in previous studies exhibited poor stability to water, further is prone to

structural changes, which may restrict their practical application.³⁵ Similarly, zeolite readily takes up water due to their hydrophilic nature, then the adsorbed water promotes hydrolysis of Si–O(H)–Al bond and induces structural changes under aqueous or humid conditions.³⁶ Carbon-based materials also strongly interact with water and the adsorbed moisture, and induce oxidation or change of pore structure under humid environments.³⁷ To improve their water stability, diverse surface modifications of support materials have been studied to tailor hydrophobicity. In MOFs, post-synthetic treatments such as alkyl-group incorporation and silylation have been employed, yet these approaches often lead to reduced specific surface area and pore size.³⁸ Zeolites have also been modified by surface grafting of organosilanes onto silanol groups, which is accompanied by a reduction in pore volume and specific surface area.³⁹ Activated carbon has similarly been silylated to provide hydrophobicity, although such modifications can induce moisture-related pore structure changes and diminish adsorption performance.⁴⁰ To overcome the side-effect of surface modification, applying hydrophobic polymer framework to form composite catalyst has been proposed recently, as polymer matrices can provide structural stability and chemical functionality in hybrid system.⁴¹ Pt/styrene–divinylbenzene copolymer⁴² and Pt/carbon black/polytetrafluoroethylene⁴³ significantly improve structural stability. However, these composite catalysts still exhibit non-uniform distribution and surface aggregation of Pt.⁴⁴ Collectively, these limitations highlight a fundamental challenge in existing hydrophobic LPCE catalysts: achieving a balanced integration of water stability, efficient mass transport, and uniform dispersion of active Pt sites without compromising structural integrity or porosity. Therefore, a novel design of catalyst is required to enhance hydrophobicity while optimizing the performance of hydrogen isotope exchange reaction. The polydimethylsiloxane (PDMS) was selected as the hydrophobic framework material due to its unique combination of high hydrophobicity, exceptional gas permeability, and chemical stability under LPCE conditions.⁴⁵ Unlike conventional hydrophobic polymers such as fluoropolymers (e.g., Teflon), which can limit mass transfer due to their dense and rigid structure, PDMS exhibits high hydrogen permeability, facilitating efficient transport of H₂ to the active Pt sites.⁴⁶ In addition, its elastomeric nature enables conformal coating on the catalyst surface, preserving active site accessibility while providing a stable hydrophobic environment.⁴⁷ These properties make PDMS particularly well-suited for maintaining an effective gas–liquid–solid interface and enhancing catalytic performance in LPCE systems.

In this study, the composite based on Pt decorated mesoporous silica and PDMS is fabricated and applied to LPCE process to design the hydrophobic catalyst for durable and efficient separation of hydrogen isotopes. Mesoporous silica has a high specific surface area and abundant surface hydroxyl groups that provide available space for uniform modification and dispersion of Pt.⁴⁸ In addition, the relatively wide mesopores avoid severe diffusion limitation, thereby offering active transport aligned with the operating conditions of this study.⁴⁹ Hydrophobicity and catalyst stability are achieved by



employing PDMS as a framework to prevent liquid water infiltration, while ensuring sufficient exposure of Pt active sites, thereby ensuring stable catalytic activity in the LPCE process. Ultimately, this enables to improve separation techniques of hydrogen isotopes by efficient and stable catalytic performance under diverse liquid-phase exchange conditions.

Experimental

Materials

The following chemicals and gases were used as received without further purification. Tetraethyl orthosilicate (TEOS, 98%), cetyltrimethylammonium bromide (CTAB, > 98%), ethanol (EtOH, 99.99%) and ammonium hydroxide solution (NH₄OH, 28.0–30.0 wt%) were purchased from Sigma-Aldrich. Tetraamineplatinum (II) nitrate (Pt(NH₃)₄(NO₃)₂) was purchased from Alfa Aesar. PDMS (Sylgard® 184), including a silicone elastomer base and its curing agent, was purchased from Dow Corning. Deionized (DI) water was supplied from Direct-Q® 3 water purification system with resistivity of 18.2 MΩ cm at 25 °C. The stainless steel Dixon ring (KT-DR) with 3 mm of diameter and height for hydrophilic column packing was also purchased from Beihai Kaite Chemical Packing Co., Ltd. H₂ (99.999%) and nitrogen gas (N₂, 99.999%) were purchased from Daesung Industrial Gases Co., Ltd. Air (78% of N₂, 21% of O₂ and around 0.9% of trace amounts of other gases) was purchased from Joongang Industrial Gases Co., Ltd. and argon gas (Ar, 99.999%) was obtained from Sejong Industrial Gases Co., Ltd.

Preparation of mesoporous silica powder

Mesoporous silica was prepared according to a previously reported method.⁴⁰ CTAB (2.4 g) was dissolved in the equivolume mixture of DI water (50 mL) and ethanol (50 mL). After 10 min of vigorous stirring, NH₄OH (12 mL) was added (Fig. 1a). Subsequently, TEOS (3.4 g) was drop-wisely dispersed into the solution mixture (Fig. 1b). The mixed solution was additionally stirred for another 2 h until it converted as gel (Fig. 1c). The molar composition of the final gel is TEOS: 0.43 CTAB: 12.5 NH₃: 54.3 EtOH: 416 H₂O. The resulting gel was washed 5 times with DI water and solid/liquid was separated by centrifugation at each cycle. Then, the resulting solid was dried in the oven at 65 °C overnight. The CTAB template, structure-directing agent, was removed by calcination at 550 °C with a heating rate of 1 °C min⁻¹ for 6 h under stagnant air conditions in the furnace (Fig. 1d). The prepared mesoporous silica powder is denoted as SiO₂.

Decoration of Pt on mesoporous silica powder

To impregnate Pt onto the silica framework, 0.52 g of Pt(NH₃)₄(NO₃)₂ was thoroughly mixed with 5.0 g of prepared mesoporous silica, resulting a 5 wt% Pt loading. Subsequently, 9.6 mL of DI water, corresponding to 1.2 times of the mesopore volume (measured by N₂ physisorption), was slowly and drop wisely added to the mixture while continuous spatula mixing at room temperature to ensure homogeneous dispersion. Then, the Pt(NH₃)₄(NO₃)₂ infiltrated into the surface and pores of mesoporous silica during drying. The dried sample was calcined under the air flow at 400 °C with a heating rate

of 2 °C min⁻¹ for 6 h. This decomposed the Pt precursor ligands formed Pt oxide, which was stably incorporated onto the surface and pores of mesoporous silica. Following calcination, the sample was purged with an Ar gas for 30 min to remove residual air and volatile impurities. Afterward, it was reduced by H₂ under same heating rate and temperature conditions, which converted Pt oxide into metallic Pt and integrated it uniformly into the mesoporous silica (Fig. 1e). The final catalyst powder was denoted as Pt@SiO₂.

Fabrication of catalytic composite based on Pt@SiO₂ and PDMS

Silicone elastomer base and its curing agent were mixed with a weight ratio of 5:2, corresponding to 2.9 g of elastomer base and 1.1 g of its curing agent, until a uniform mixture was obtained. Then, 1.0 g of Pt@SiO₂ was added and manually mixed for 10 min to ensure even distribution. The mixture was degassed under 1.3 kPa at room temperature for 10 min to eliminate air bubbles causing potential discontinuity of final catalyst. After degassing, the mixture was poured into a lattice mold, consisting of multiple trapezoidal prisms with dimensions of 2.1 mm of top base, 3.6 mm of bottom base and 1.2 mm of height, without overflow (Fig. 1f). After curing at 60 °C for 4 h, the composite was carefully recovered from the mold (Fig. 1g). The resulting composite, denoted as Pt@SiO₂-PDMS, had 1 wt% of Pt loading. Additionally, pristine PDMS and mesoporous silica incorporated PDMS were fabricated without Pt decoration procedure. Each product is denoted as PDMS and SiO₂-PDMS.

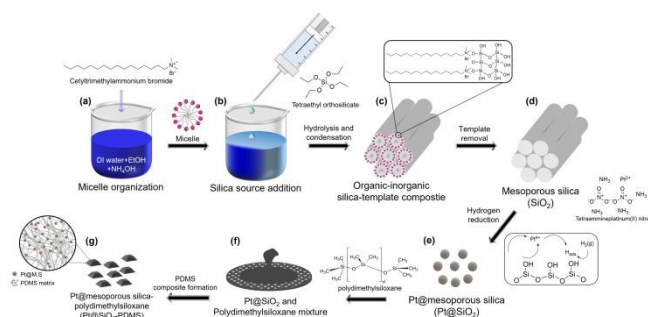


Fig. 1 The schematic diagram of the fabrication process for the Pt@SiO₂-PDMS. (a) Formation of micelles with CTAB as a structure-directing agent in a solution containing DI water, EtOH and NH₄OH; (b) Addition of TEOS as the silica source into the solution mixture; (c) Formation of a silica-template composite structure through TEOS-induced hydrolysis and condensation; (d) Template removal by calcination activating well-ordered mesopores with uniform manner; (e) Deposition of Pt onto the mesoporous silica framework through H₂ reduction; (f) Homogeneously mixed PDMS and Pt@SiO₂ mixture in the mold for curing; (g) Final catalyst composite, Pt@SiO₂-PDMS.

Characterizations

The X-ray diffraction (XRD) patterns of the powder samples were measured using a D2 PHASER (Bruker) from 0 to 8° (low angle) and 10 to 80° (high angle) of 2θ at a rate of 0.002° per step with a counting time of 0.5 s per step using a Cu-Kα radiation source. The scanning electron microscopy (SEM) images were obtained SU-8020 (Hitachi) at a landing energy of 15 kV. The powder and composite



samples were prepared on the top of carbon tape and coated with gold to avoid surface discharge. Transmission electron microscopy (TEM) coupled with energy-dispersive X-ray spectroscopy (EDS) analyses were performed using a JEM-2100F (JEOL) operated at an accelerating voltage of 200 kV. The powder samples were prepared by dispersing in ethanol and drop-casting the suspension onto a carbon-coated Cu grid, followed by natural drying. The N₂ physisorption isotherms were measured at -196 °C using an Autosorb iQ-XR Viton (Quantachrome). Before measurement, the powder samples were degassed overnight at 150 °C under vacuum to remove the pre-adsorbed gases, moisture and other impurities. The N₂ physisorption isotherms were analyzed to specify the pore volume, specific surface area and pore size distribution (PSD). The specific surface area was determined by the Brunauer-Emmett-Teller (BET) method and the PSD was determined by Broekhoff-de Boer/Frenkel-Halsey-Hill (BdB-FHH) method. The Pt content in Pt@SiO₂ was measured using the inductively coupled plasma optical emission spectrometry (ICP-OES) with an Avio 500 (Perkin Elmer). The Pt@SiO₂ was digested by microwave-assisted acid digestion using aqua regia mixed with hydrofluoric acid, followed by treatment at 230 °C for 30 min in an ultraWAVE system (Milestone). The morphology of the fabricated PDMS, SiO₂-PDMS, Pt@SiO₂-PDMS and Dixon ring was observed using a stereomicroscopy (M205 C, Leica) equipped with the MC170 HD camera. The Fourier transform-infrared/attenuated total reflectance (FT-IR/ATR) spectra of the samples were measured using a Nicolet iS5 (Thermo Fisher Scientific). The spectra were recorded in the range of 500–4000 cm⁻¹ at a resolution of 4 cm⁻¹. The wettability of the fabricated catalytic composites was evaluated by measuring the water contact angle (WCA) using a Cam 200 (KV Instruments). H₂ chemisorption measurements were carried out using an AutoChem II 2920 (Micromeritics). Prior to the measurement, the samples were treated under a 10% H₂/argon (Ar) flow at 180 °C for 30 min with a heating rate of 10 °C min⁻¹. The samples were then cooled to 40 °C under flowing Ar, followed by Ar purge for 10 min. Subsequently, H₂ pulse chemisorption was conducted at 40 °C, and the amount of chemisorbed H₂ was used to determine the metal dispersion of Pt. Thermogravimetric analysis (TGA) was performed using a SETSYS Evolution TGA (Setaram Instrumentation). 3 mg of Pt@SiO₂-PDMS samples were heated from room temperature to 800 °C at a heating rate of 10 °C min⁻¹ under Ar with a flow rate of 50 mL min⁻¹.

Liquid phase catalytic exchange performance

The catalytic reactor, as shown in Fig. S2 of Supplementary Information, was designed as a glass column with an inner diameter of 15 mm and a length of 175 mm. The exterior of the column was insulated to maintain reaction temperature by circulating water coming from water bath which was also controlled under reaction temperature. The top of the column was connected to a peristaltic pump, allowing the liquid water (DI water) to flow at a constant rate. The liquid water in a 2 L beaker on a hot plate and the connecting tubing by wrapping it with heating tape were pre-heated to the reaction temperature. At the bottom of the column, a gas inlet was connected to supply N₂ or H₂ gas, with flow rates controlled by a

mass flow controller. The liquid outlet of the column was narrow glass tube, where the packing structure prevented the loss of the catalyst composites and Dixon rings, allowing only the liquid to discharge. The top of the column was designed with a gas outlet to vent the reacted gas. Before and after running, the column interior was purged with N₂ gas at a flow rate of 2 standard liters per minute (SLPM) for 10 min. The LPCE performance was evaluated with a H₂ (g) flow rate of 0.365 SLPM and a DI water flow rate of 0.3 mL min⁻¹. This is 1:1 mole ratio of hydrogen in gas and liquid. The catalyst bed consisted of randomly packed catalyst and Dixon rings with a fixed bed length of 155 mm and the catalytic performance was tested under various volume ratios of 1:4, 1:1 and 2:1 at temperature ranging from 30 to 80 °C. The liquid samples were collected every 30 min in the liquid outlet for 180 min. For long-term performance, test was conducted with a packing volume ratio of 2:1 using a mixture of catalyst and Dixon rings at 80 °C for 14 days. The liquid samples were collected every 24 h. After each cycle, the column containing catalyst and Dixon rings was stored in a 65 °C oven overnight for regeneration before the recyclability test. Column efficiency (η) was evaluated using the following Equation (1):

$$\eta \equiv \frac{y_{out} - y_{in}}{y_{out}^* - y_{in}} \times (1)$$

Here, y_{in} represents the atomic concentration of D at the gas inlet. The isotopic compositions x_{in} and x_{out} correspond to the atomic concentration of D at the liquid inlet and outlet were experimentally measured. The gas-phase outlet composition y_{out} was determined from a mass-balance calculation using x_{in} and x_{out} . The theoretical outlet composition y_{out}^* was calculated using the temperature-dependent water–hydrogen equilibrium constant.²⁴ The D concentrations in the H₂ gas and DI water were 135 $\mu\text{mol mol}^{-1}$ (D/(D + H)) and 147 $\mu\text{mol mol}^{-1}$ (D/(D + H)), respectively. For the H₂ gas, the D concentration was measured with a quadrupole mass spectrometer using the PrismaPro® QMG 250 M1 (Pfeiffer Vacuum GmbH). The D concentration in the liquid samples was determined with a cavity ring-down spectroscopy using the L2140-i (PICARRO).

Results and discussion

Characterization of Pt@SiO₂

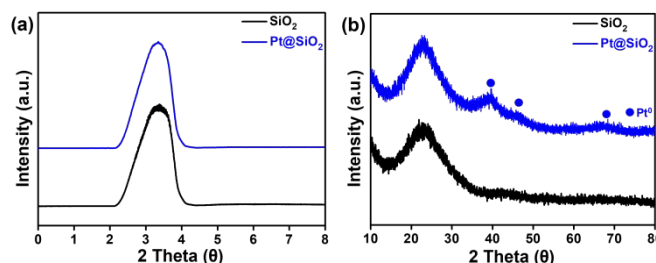


Fig. 2 The (a) low- and (b) high-angle XRD patterns of SiO₂ and Pt@SiO₂.

Fig. 2 shows the XRD patterns of SiO₂ and Pt@SiO₂. As presented in Fig. 2a, both display a low-angle diffraction peak at $2\theta = 3.3^\circ$, indicating the presence of an ordered mesoporous structure.⁴¹ The



preservation of this peak even after Pt decoration suggests that the mesopore structure of the silica remains without collapse. In Fig. 2b, a broad peak at $2\theta = 21\text{--}23^\circ$ is observed, indicating the amorphous nature of mesoporous silica. For Pt@SiO₂, additional peaks appear at $2\theta = 39.8, 46.3$ and 67.8° , which are attributed to metallic Pt⁰. Overall, Pt was successfully decorated without any significant change on the mesoporous structure of the support.⁴²

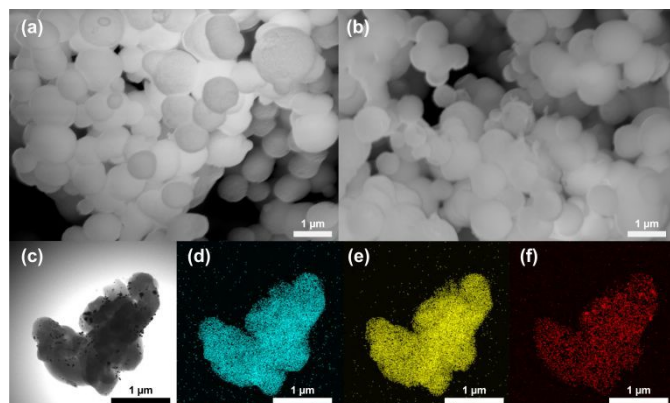


Fig. 3 SEM images of (a) SiO₂ and (b) Pt@SiO₂. TEM image of (c) Pt@SiO₂ and its EDS elemental mapping of (d) O, (e) Si and (f) Pt.

Figs. 3a and 3b display SEM images of SiO₂ and Pt@SiO₂. They exhibit the spherical morphology commonly observed in a novel synthesis of mesoporous silica.⁴⁰ The particle sizes are ranging approximately from 200 to 900 nm, without any noticeable difference after Pt decoration. Fig. 3c presents the TEM image of Pt@SiO₂, in which homogeneously dispersed Pt is observed within the mesoporous silica framework. Correspondingly, the EDS elemental mappings of Si, O and Pt (Figs. 3d–f) show uniform Si and O originating from mesoporous silica and a homogeneous distribution of Pt. Thus, the presence and dispersion of Pt followed by Pt decoration is visually as well as elementally validated, which is consistent with crystallography result in Fig. 2.

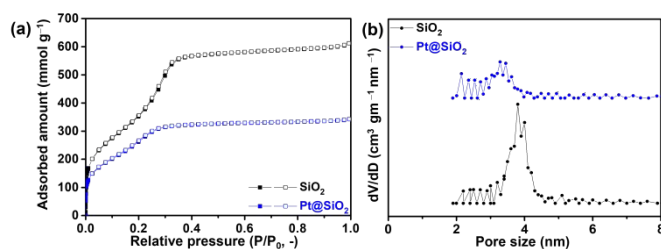


Fig. 4 (a) N₂ physisorption isotherms for SiO₂ and Pt@SiO₂ at -196°C (filled square: adsorption; open square: desorption) and (b) pore size distributions for SiO₂ and Pt@SiO₂ calculated by the BdB-FHH method.

Fig. 4 and Table 1 present the N₂ physisorption isotherms and textural property of SiO₂ and Pt@SiO₂. In Fig. 4a, they exhibit Type IV isotherms in IUPAC classification, which stands for typical mesoporous structure. The adsorption capacity decreased from 612 to 342 mmol g⁻¹ after Pt decoration on SiO₂. This reduction indicates partial blockage or narrowing of the pore structure. In Fig. 4b, SiO₂

shows a PSD centered at 3.8 nm. After Pt loading, the main peak is slightly shifted to 3.5 nm and its intensity significantly decreases. This is well coincided with the reduction of adsorption capacity. According to Table 1, the BET surface area and pore volume also decrease from 1800 to 710 m² g⁻¹ and 0.80 to 0.53 cm³ g⁻¹ after Pt decoration, respectively. Since the pore size ranging from 3.0 to 3.9 nm still remains within the mesopore, the mesoporous silica framework is preserved after Pt decoration. Based on the ICP-OES results, the Pt content in Pt@SiO₂ was determined to be 5.12 wt%, which closely matches the intended loading of 5.00 wt%. Overall, Pt is successfully incorporated into the mesoporous silica framework.

Table 1 Textural property of SiO₂ and Pt@SiO₂.

	BET surface area (m ² g ⁻¹)	Pore volume (cm ³ g ⁻¹)	Pore size (nm)
SiO ₂	1800	0.83	3.3–4.3
Pt@SiO ₂	710	0.53	3.0–3.9

Characterization of Pt@SiO₂-PDMS

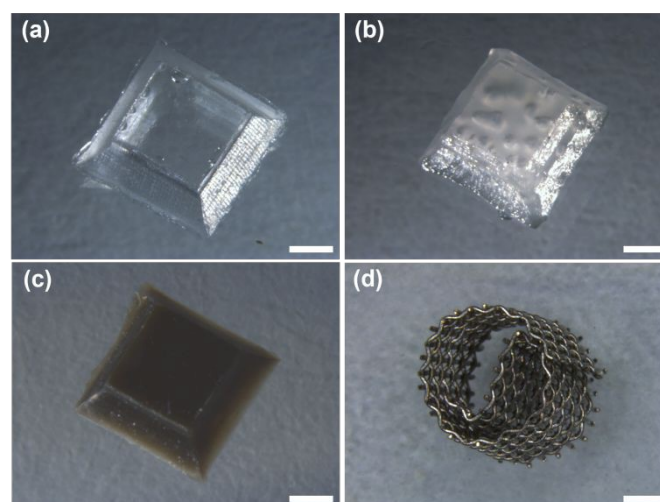


Fig. 5 The stereomicroscopy images of (a) PDMS, (b) SiO₂-PDMS, (c) Pt@SiO₂-PDMS and (d) Dixon ring (scale bar is 1 mm).

Fig. 5 presents stereomicroscopy images of PDMS, SiO₂-PDMS, Pt@SiO₂-PDMS and a Dixon ring. The Dixon ring is used as a hydrophilic packing material in our LPCE process. The composite morphology and packing structure are clearly distinguishable and can be visually identified. Pristine PDMS in Fig. 5a shows a transparent and smooth surface with uniform appearance, reflecting its homogeneous molecular arrangement and flexibility.⁴³ The SiO₂-PDMS in Fig. 5b appears white and opaque due to the uniform dispersion of mesoporous silica particles within the PDMS polymer matrix. Fig. 5c shows the Pt@SiO₂-PDMS with a dark brown color close to black. This is because the presence of metallic Pt supported on silica and suggests its uniform distribution within the PDMS matrix demonstrated in Fig. 3. Moreover, cross-sectional SEM image (Fig. S3 of Supplementary Information) indicates that Pt@SiO₂ is well incorporated within the PDMS matrix. Fig. 5d presents the Dixon ring



composed of a regular stainless steel mesh. It promotes vapor liquid equilibrium, here the equilibrium between $\text{H}_2\text{O}(\text{v})$ and $\text{H}_2\text{O}(\text{l})$. Further, this enhances interfacial contact, which reduces mass transfer resistance during the isotope exchange process.⁴⁴

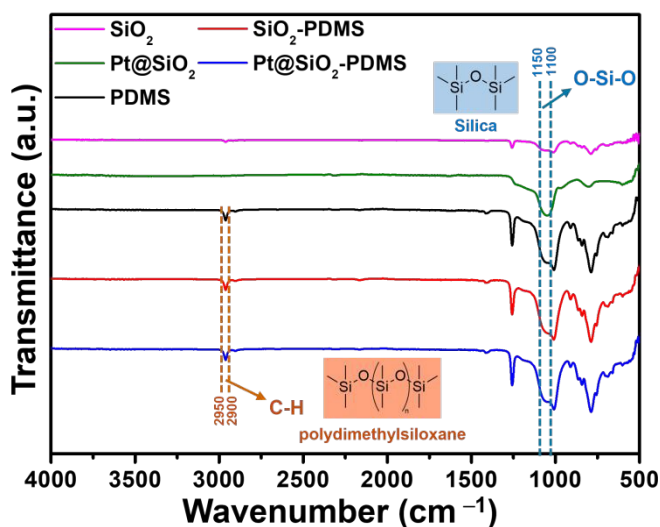


Fig. 6 FT-IR/ATR spectra of SiO_2 , Pt@SiO_2 , PDMS, SiO_2 -PDMS and Pt@SiO_2 -PDMS.

Fig. 6 presents the FT-IR/ATR spectra of SiO_2 , Pt@SiO_2 , PDMS, SiO_2 -PDMS and Pt@SiO_2 -PDMS, obtained to investigate the surface and near-surface chemical structures. In SiO_2 , a strong asymmetric Si–O–Si stretching band is observed in the range of 1100–1150 cm^{-1} , corresponding to the primary bonding network within the silica framework.⁴⁵ For Pt@SiO_2 , the same band appears with increased intensity and a slight shift toward lower wavenumbers, which indicates structural modification induced by Pt decoration.⁴⁶ The spectrum of PDMS shows C–H stretching band in the range of 2900–2950 cm^{-1} , representing the presence of methyl groups in the polymer structure. This peak is also observed in the SiO_2 -PDMS, suggesting that the organic structure of PDMS stably remains after silica incorporation.⁴⁷ In the Pt@SiO_2 -PDMS, both the Si–O–Si and C–H stretching bands are clearly retained, indicating the coexistence of organic and inorganic hybrid components. These results indicate that the structural features of PDMS and SiO_2 are preserved near the surface. Also, the Pt decoration and composite formation does not disrupt the integrity of each component.

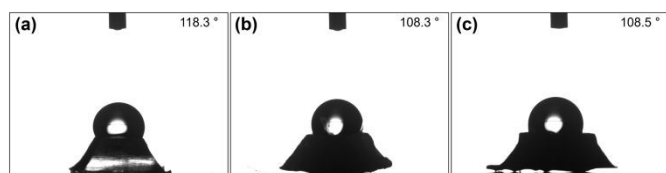


Fig. 7 The WCA of (a) PDMS, (b) SiO_2 -PDMS, (c) Pt@SiO_2 -PDMS.

Fig. 7 presents the WCA of PDMS, SiO_2 -PDMS and Pt@SiO_2 -PDMS to evaluate their surface wettability. Surface wettability is a critical parameter that influences the interaction between the catalyst and liquid reactants. In the LPCE process, an excessively hydrophilic surface may lead to the accumulation coverage of water due to

reaction on the catalyst composite surface, potentially causing catalyst poisoning.²⁸ Therefore, possessing appropriate hydrophobicity is necessary for maintaining catalyst activity and operational stability. As shown in Fig. 7a, the pristine PDMS exhibits a high WCA of 118.3°, which is attributed to abundant methyl groups.⁴⁸ The SiO_2 -PDMS (Fig. 7b) has a slightly reduced WCA of 108.3°, which is associated with the incorporation of hydrophilic SiO_2 particles within the PDMS matrix. The Pt@SiO_2 -PDMS (Fig. 7c) has a similar WCA of 108.5°, indicating that the decoration of Pt does not affect the intrinsic surface wettability of the SiO_2 -PDMS. The surface wettability suggests that the PDMS-based composites maintain an appropriate hydrophobic surface suitable for efficient isotope exchange under liquid-phase conditions.

In Table 2, H_2 chemisorption analysis showed a metal dispersion of 3.5%, corresponding to a metallic surface area of 8.6 $\text{m}^2 \text{g}^{-1}$ metal and an average particle size of 32.4 nm. It should be noted that the H_2 chemisorption measurements primarily reflect the fraction of Pt sites accessible to H_2 under the measurement conditions (40 °C, pulse chemisorption). In our Pt@SiO_2 -PDMS system, Pt species partially embedded within the PDMS layer may not be fully probed, potentially leading to an underestimation of the actual dispersion. To further evaluate batch-to-batch reproducibility of Pt@SiO_2 -PDMS, TGA was performed as shown in Fig. S4 of Supplementary Information. Two difference Pt@SiO_2 -PDMS from different batch shows 20.5 and 20.7% of weight loss which are marginally identical. This guarantees the reproducibility of Pt@SiO_2 -PDMS.

Table 2 H_2 chemisorption results of Pt@SiO_2 -PDMS.

Metal dispersion (%)	Metallic surface area ($\text{m}^2 \text{g}^{-1}$ metal)	Particle size (nm)
3.5	8.6	32.4



Liquid phase catalytic exchange performance

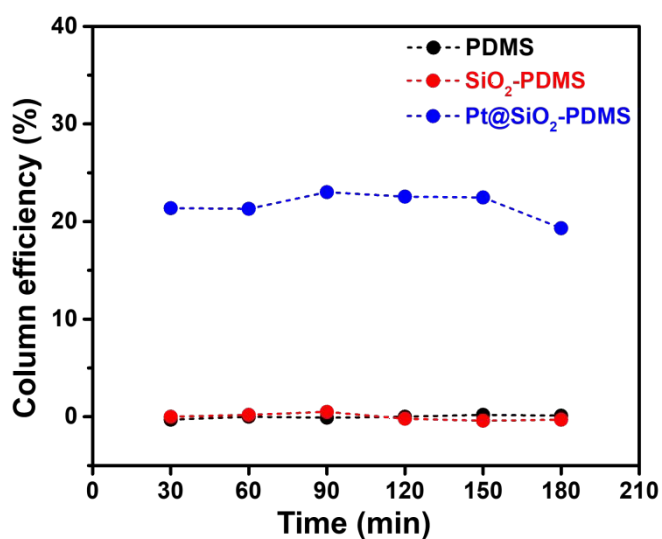


Fig. 8 Column efficiency (%) of PDMS, SiO₂-PDMS and Pt@SiO₂-PDMS randomly packed with Dixon rings in a volume ratio of 1:4 measured at 60 °C.

Fig. 8 demonstrates the column efficiency (%) of the PDMS, SiO₂-PDMS and Pt@SiO₂-PDMS randomly packed with Dixon rings in a volume ratio of 1:4 measured every 30 min interval over 180 min at 60 °C. The corresponding percentage values are summarized in Table S1 of Supplementary Information. Both PDMS and SiO₂-PDMS exhibited negligible column efficiency over the 180 min reaction period. In contrast, the Pt@SiO₂-PDMS clearly demonstrated catalytic activity. It reached a maximum column efficiency of 23.0% at 90 min of reaction time and maintained values around 20% steadily up to 180 min. This indicates that the newly developed Pt@SiO₂-PDMS effectively promotes the hydrogen isotope exchange reaction, facilitating the transfer of D from the liquid to gas phase.

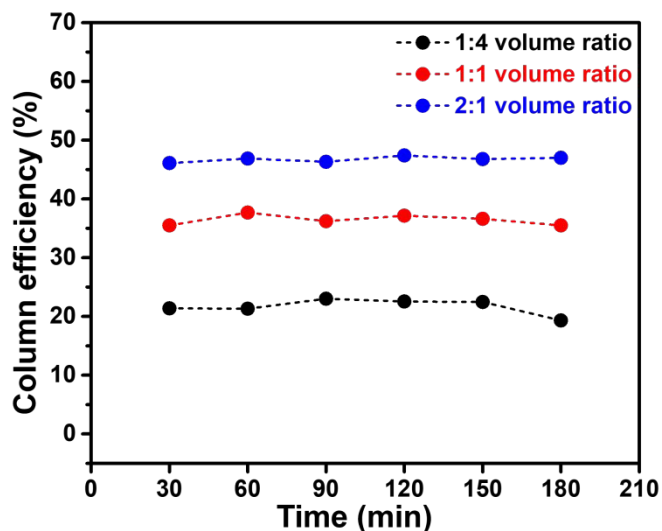


Fig. 9 Column efficiency (%) of the Pt@SiO₂-PDMS randomly packed with Dixon rings in a volume ratio of 1:4, 1:1 and 2:1 measured every 30 min interval over 180 min at 60 °C.

Fig. 9 displays the column efficiency of the Pt@SiO₂-PDMS randomly packed with Dixon rings in a volume ratio of 1:4, 1:1 and 2:1 measured every 30 min interval over 180 min at 60 °C. The corresponding percentage values are summarized in Table S2 of Supplementary Information. When the catalyst amount increases from the ratio 1:4 to 1:1, the overall column efficiency increases around 14.8% and maximum value is 37.7% at 60 min. Further increasing the catalyst amount ratio from the ratio 1:1 to 2:1, the overall column efficiency further increases around 10.3% and the highest efficiency of 47.4% at 120 min. This trend indicates that increasing the catalyst amount enhances the catalytic efficiency of the LPCE column. In conventional LPCE processes, the gas-liquid interfacial area is largely fixed by the packing configuration, thereby increasing the catalyst fraction alone does not guarantee proportional improvement in column efficiency.²¹ In the present LPCE process, the performance enhancement observed is attributed to the greater availability of active Pt and the expanded interfacial contact between the catalyst and reactants, H₂O(l) and H₂(g), thereby reducing mass transfer resistance and promoting the hydrogen isotope exchange reaction.²¹ Across every volume ratio, the column efficiency stably maintained over the 180 min reaction period within standard deviation of ±0.4–1.2%. This demonstrates that the Pt@SiO₂-PDMS maintained both activity and durability under the tested conditions.

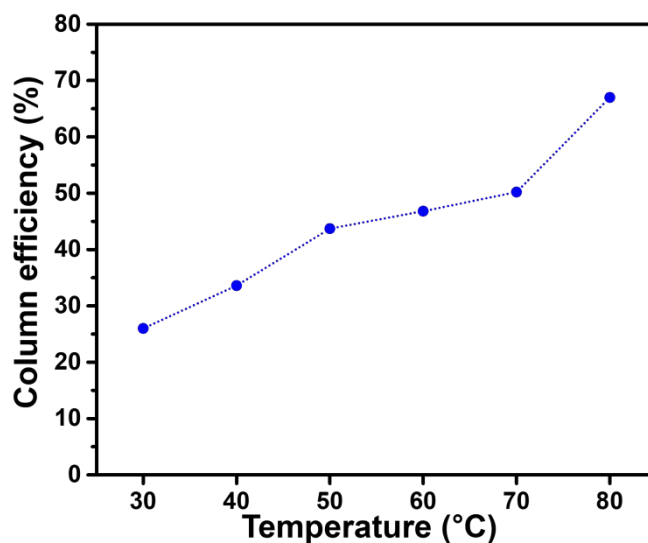


Fig. 10 Column efficiency (%) of the Pt@SiO₂-PDMS randomly packed with Dixon rings in a volume ratio of 2:1 measured at 180 min under temperature ranging from 30 to 80 °C.

With the volume ratio of 2:1 having the highest column efficiency, Fig. 10 presents the column efficiency of the Pt@SiO₂-PDMS measured at 180 min under temperatures ranging from 30 to 80 °C. Detailed time-dependent profiles are provided in Fig. S5 of Supplementary Information and the corresponding percentage values are summarized in Table S3 of Supplementary Information. Between 30 and 70 °C, the column efficiency enhanced with increasing temperature while maintaining stable profiles over 180 min. The maximum efficiencies in each temperature were 28.7%



(30 °C, 60 min), 33.6% (40 °C, 150 min), 46.0% (50 °C, 60 min), 48.8% (60 °C, 30 min) and 54.2% (70 °C, 60 min). Throughout the entire reaction time, the column efficiencies maintained relatively stable, exhibiting only minor fluctuations within a standard deviation range of ± 0.2 – 1.8% at the temperature ranging from 30 to 70 °C. On the other hand, the catalyst exhibited the much better performance at 80 °C. The efficiency increased as the reaction time, reaching 67.7% at 180 min. Overall, it has minor fluctuations within a standard deviation of $\pm 2.4\%$, indicating stable and steady catalytic exchange reaction. This temperature-dependent trend suggests that the hydrogen isotope exchange reaction is governed by reaction kinetics, where increasing temperature promotes more frequent and energetic molecular collisions, thereby accelerating the D–H exchange.⁴⁹ The catalyst retained its activity under tested temperature conditions and the excellent performance observed at 80 °C. Thus, this condition is selected for the subsequent long-term durability evaluation to evaluate feasibility of industrial application.

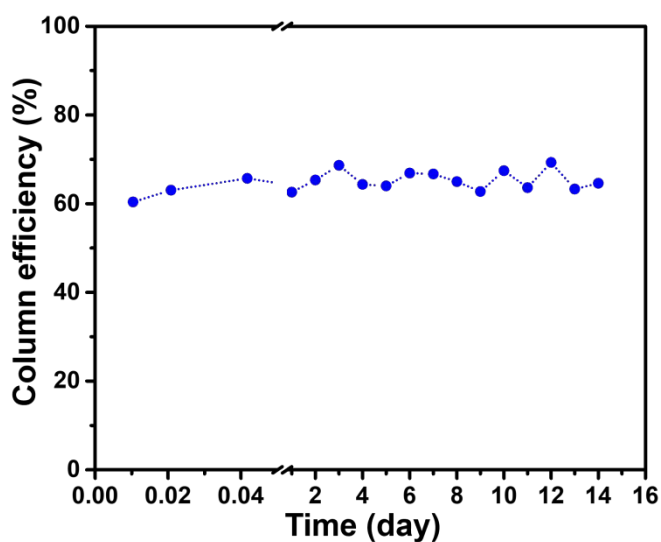


Fig. 11 Column efficiency (%) of the Pt@SiO₂-PDMS randomly packed with Dixon rings in a volume ratio of 2:1 measured for 14 days at 80 °C.

With the optimized volume ratio and temperature, the long-term operational stability of the Pt@SiO₂-PDMS was evaluated under continuous LPCE operation for 14 days at 80 °C (Fig. 11). The corresponding column efficiency values are summarized in Table S4 of Supplementary Information. Throughout the entire test period, the column efficiency fluctuated slightly around an average value of $64.9 \pm 2.3\%$, indicating stable catalytic performance without noticeable deactivation. Minor variations were observed around day 3 and 12, during which the efficiency temporarily increased to 69.3% and subsequently returned to the average level. This stable efficiency profile demonstrates that the Pt active sites were effectively protected by the PDMS matrix during prolonged liquid-phase operation. After 14 days of LPCE operation and subsequent regeneration, recyclability was evaluated under same conditions as Fig. 9 to make sure the stability of the catalytic performance (Fig. S6 of Supplementary Information). The corresponding percentage

values are summarized in Table S5 of Supplementary Information, providing an average column efficiency of $45.6 \pm 1.1\%$ over 180 min. This is consistent with the values obtained in Fig. 9, thereby demonstrates stable and consistent catalytic performance under repeated operation. In addition, the hydrophobic characteristic of the catalyst was maintained with a WCA of 102.8° after the LPCE test (Fig. S7 of Supplementary Information). This value is comparable to that of the fresh catalyst (108.5°), indicating that the hydrophobicity of Pt@SiO₂-PDMS is well preserved after long-term operation, with the surface functional groups of the PDMS framework remaining stable under LPCE condition. H₂ chemisorption results of the used catalyst after long-term operation (Table S6 of Supplementary Information) show a metal dispersion of 3.1%, a metallic surface area of 7.6 m² g⁻¹ metal, and a Pt particle size of 36.7 nm. This is comparable to those of the fresh catalyst which were 3.5%, 8.6 m² g⁻¹ metal, and 32.4 nm, respectively. Thus, it demonstrates that the catalytic structure is well preserved. The LPCE process itself is preserved.

In Table 3, the Pt@SiO₂-PDMS catalyst is compared with previously reported Pt-based catalysts for hydrogen isotope exchange in the LPCE process. The Pt@SiO₂-PDMS catalyst shows column efficiencies of 49–68% at 60–80 °C, while Pt/200-S-NH₂-GR exhibits 75–90% at 40–60 °C,⁶⁰ Pt@MIL-101/PVDF shows 75% at 60 °C,⁶¹ and Pt_{0.5}Ru_{0.5}/C exhibits 72–88% at 50 °C.⁶² Pt@SBA-15-Tetramethyldisilazane and Pt/s-C₃N₄-7 also show efficiencies of 63–73% and 64–85% over 30–70 °C and 40–80 °C, respectively.^{33,44} The Pt@SiO₂-PDMS catalyst exhibits relatively lower column efficiency under similar operating conditions such as column diameter, height, and particularly temperature. This difference is attributed to the limited availability of exposed Pt active sites evidenced by large Pt particle size. The H₂ chemisorption of Pt@SiO₂-PDMS shows a low metal dispersion (3.1%) and relatively large Pt particle size (~36.7 nm) as shown in Table 2. Significant work remains to be done in optimizing mesoporous silica materials and Pt decoration techniques tailoring better control of metal dispersion and Pt particle size suited for increasing the number of accessible active sites. Despite the relatively lower column efficiency, the catalyst can be prepared through simple fabrication procedure using mesoporous silica and PDMS with laboratory scale LPCE column, offering advantages in terms of cost and scalability. The LPCE process itself is successfully demonstrated under the present conditions, and further studies should focus on scale up of process coupled with optimization of catalyst fabrication.

Conclusions

The Pt@SiO₂-PDMS was successfully fabricated by decorating Pt on a mesoporous silica framework followed by embedding within a PDMS matrix. The catalyst demonstrated high column efficiency and stability for the hydrogen isotope exchange reaction in the LPCE process. The highest performance was achieved when Pt@SiO₂-PDMS was randomly packed with Dixon rings in a volume ratio of 2 : 1



ARTICLE

Table 3 Summary of previously reported Pt-based catalysts for hydrogen isotope exchange in the LPCE process

Catalyst	Column diameter (mm)	Column height (mm)	Pt particle size (nm)	Operating temperature (°C)	Column efficiency (%)	References
Pt@SiO ₂ -PDMS	15	155	32.4	30–80	29–68	This work
Pt/200-S-NH ₂ -GR ^a	38	32.2	1.85 ±0.35	40–60	75–90	60
Pt@MIL-101/PVDF ^b	25	450	2.9	60	75	61
Pt _{0.5} Ru _{0.5} /C ^c	16	450	1.9 ±0.5	50	72–88	62
Pt@SBA-15-Tetramethyldisilazane ^d	15	350	2.03	30–70	63–73	33
Pt/ <i>s</i> -C ₃ N ₄ -7 ^e	0.65 (cross-section)	630	0.82 ±0.08	40–80	64–85	44

^aPt/200 μm trimethoxyoctylsilane dual modified 2-dimensional aminated graphene; ^bPt@MIL-101/polyvinylidene fluoride;

^cPt_{0.5}Ruthenium_{0.5}/carbon; ^dPt@Santa Barbara Amorphous-15-Tetramethyldisilazane; and ^ePt/PDMS modified carbon nitride-7 (7 stands for the theoretical mass percentage of Pt in catalyst)

and measured at 80 °C, resulting in a column efficiency of 67.7% with a catalyst bed length of 155 mm. The stable column efficiency observed up to 14 days of continuous operation indicated that the Pt@SiO₂-PDMS retained its hydrophobicity and structural integrity without noticeable deactivation or poisoning. The enhanced performance is attributed to the effective exposure of Pt active sites and the hydrophobic surface provided by the PDMS matrix, which minimized liquid water penetration and preserved catalytic activity. These results demonstrate that the Pt@SiO₂-PDMS serves as a durable and efficient catalyst for the LPCE process, enabling long-term hydrogen isotope exchange from liquid to gas phase. This study provides a promising platform for designing hydrophobic composite catalysts applicable to the sustainable and scalable hydrogen isotope exchange process. Further, hydrophobic composite catalysts can be

extended to catalytic systems requiring stable operation under moisture-rich conditions, including hydrogen purification and gas-phase reaction processes.

Author contributions

Daeuk Kang: Data Curation, Investigation, Methodology, Writing – original draft, Writing – review & editing. **Huiryung Heo:** Investigation, Methodology. **Euna Jeong:** Investigation. **Hee-Man Yang:** Conceptualization. **Dong-Yeun Koh:** Funding acquisition. **Chan Woo Park:** Conceptualization, Funding acquisition, Project administration, Supervision, Writing – review & editing. **Hyung-Ju Kim:** Conceptualization, Investigation, Methodology, Resources, Supervision, Writing – original draft, Writing – review & editing.



Conflicts of interest

The authors declare no conflict of interest.

Data availability

The data supporting the findings of this study are available within the article and its Supplementary Information (SI). SI is available. See DOI: <https://doi.org/>

Acknowledgements

The authors are grateful for the financial support from National Research Foundation of Korea (NRF) grant funded by the Korea government (MSIP) (No. RS-2022-00155422), and from the Korea Evaluation Institute of Industrial Technology, funded by Korean government, Ministry of Trade, Industry and Energy (Grant No. 20022479). This research was also financially supported by the Institute of Civil Military Technology cooperation funded by the Defense Acquisition Program Administration and Ministry of Trade, Industry and Energy of Korea government under grant No. 22-CM-BR-14.

References

- B. Wang, X. Xiao, C. Chang, F. Huang, T. Y. K. Qin, H. He and J. Xu, *J. Mater. Chem. A*, 2025, **13**, 18081–18114.
- M. Chen, K. Zhao, J. Li, G. Lin, D. Banham, L. Du and M. Chen, *J. Mater. Chem. A*, 2025, **13**, 7687–7691.
- R. Cameron, in *Nuclear Fission Reactors*, ed. I. R. Cameron, Springer, Boston, MA, 1982, pp. 269–282.
- S. Jung, W.-L. Cheung, S. Li, M. Wang, W. Li, C. Wang, X. Song, G. Wei, Q. Song, S. S. Chen, W. Cai, M. Ng, W. K. Tang and M.-C. Tang, *Nat. Commun.*, 2023, **14**, 6481.
- X. Hou, *J. Nucl. Fuel Cycle Waste Technol.*, 2018, **16**, 11–39.
- T. Tanabe, *J. Nucl. Mater.*, 2011, **417**, 545–550.
- N. Momoshima, *Radiat. Prot. Dosimetry*, 2022, **198**, 896–903.
- Cauquoïn, M. Gusyev, H. Bong, A. Okazaki and K. Yoshimura, *Environ. Sci. Pollut. Res.*, 2025, **32**, 3649–3663.
- Chen, J. Hou, J. Li, X. Chen, C. Xiao, Q. Wang, Y. Gong, L. Yue, L. Zhao, G. Ran, X. Fu, X. Xia and H. Wang, *Fusion Eng. Des.*, 2020, **153**, 111460.
- M. Enoda, T. Yamanishi, H. Yoshida, Y. Naruse, H. Fukui and K. Muta, *Fusion Eng. Des.*, 1989, **10**, 319–323.
- K. M. Song, S. H. Sohn, D. W. Kang, S. W. Paek and D. H. Ahn, *Fusion Eng. Des.*, 2007, **82**, 2264–2268.
- E. P. Magomedbekov, I. L. Rastunova and N. N. Kulov, *Theor. Found. Chem. Eng.*, 2021, **55**, 1–11.
- M. Lozada-Hidalgo, S. Zhang, S. Hu, A. Esfandiari, I. V. Grigorieva and A. K. Geim, *Nat. Commun.*, 2017, **8**, 15215.
- H. K. Rae, in *Separation of Hydrogen Isotopes*, American Chemical Society, 1978, vol. 68, pp. 1–26. DOI: 10.1039/D6MA00202A
- M. Rethinasabapathy, S. M. Ghoreishian, S.-K. Hwang, Y.-K. Han, C. Roh and Y. S. Huh, *Adv. Mater.*, 2023, **35**, 2301589.
- G. Ana, I. Cristescu, M. Draghia, C. Bucur, O. Balteanu, M. Vijulie, G. Popescu, C. Costeanu, N. Sofilca, I. Stefan, R. Daramus, A. Niculescu, A. Oubraham, I. Spiridon, F. Vasut, C. Moraru, S. Brad and G. Pasca, *Fusion Eng. Des.*, 2016, **106**, 51–55.
- J. Hou, J. Li, C. Xiao, H. Wang and S. Peng, *Separations*, 2024, **11**, 219.
- J. L. Aprea, *Int. J. Hydrogen Energy*, 2002, **27**, 741–752.
- D.-W. Lim, J. Ha, Y. Oruganti and H. R. Moon, *Mater. Chem. Front.*, 2021, **5**, 4022–4041.
- K. D. Kok, *Nuclear Engineering Handbook*, CRC Press, Boca Raton, FL, 2nd edn., 2016.
- S. M. Mhd Yusof, S. S. M. Lock, N. N. Abdul Talib and L. C. Seng, *Sustainability*, 2024, **16**, 4796.
- H. Yamai, S. Konishi, M. Hara, K. Okuno and I. Yamamoto, *Fusion Technol.*, 1995, **28**, 1591–1596.
- A. Fedorchenko, I. A. Alekseev, S. D. Bondarenko and T. V. Vasyanina, *Fusion Sci. Technol.*, 2017, **71**, 432–437.
- J. Hou, S. Hu, L. Xiong, K. Weng, T. Yang and Y. Luo, *Processes*, 2024, **12**, 2549.
- B. Siddique, M. A. Shaheen, A. Abbas, Y. Zaman, H. M. A. Amin, M. M. Alam, N. K. Alharbi, F. Alshehri, A. Shami, F. A. Al-Joufi and A. Ali, *Int. J. Environ. Anal. Chem.*, 2025, **105**, 9414–9436.
- Jabbar, A. Abbas, N. Assad, M. Naeem-ul-Hassan, H. A. Alhazmi, A. Najmi, K. Zoghebi, M. Al Bratty, A. Hanbashi and H. M. A. Amin, *RSC Adv.*, 2023, **13**, 28666–28675.
- J. Tang, L. Shen, K. Zhao, J. Peng, Q. Chen, C. Yu, Y. Li, A. Abbas, S. Wang and Z. Liu, *Appl. Surf. Sci.*, 2024, **643**, 158574.
- G. Ionita, C. Bucur, I. Spiridon and I. Stefanescu, *J. Radioanal. Nucl. Chem.*, 2015, **305**, 117–126.
- S. H. Sohn and K. J. Lee, *J. Nucl. Sci. Technol.*, 2006, **43**, 874–883.
- H. Heo, J. Jang, E. Jeong, H.-J. Kim, Y. J. Kim, C. W. Park, J. So and D.-Y. Koh, *Energy Environ. Mater.*, 2025, **8**, e12815.
- L. He, H. Ruan, Y. Liu, Q. Jia, D. Wu, L. Huang, X. Wang and Y. Yin, *Appl. Catal. Open*, 2025, **201**, 207034.
- S. Hu, J. Hou, L. Xiong, K. Weng, T. Yang and Y. Luo, *Sep. Purif. Technol.*, 2011, **77**, 214–219.
- Z. Lu, X. Fu, J. Li, J. Hou, G. Ran, C. Xiao and X. Wang, *Int. J. Hydrogen Energy*, 2023, **48**, 1979–1987.
- L. Shen, X. Chen, Y. Chen, J. Peng, A. Abbas, J. Wei, C. Yu, J. Li and Y. Li, *J. Electron. Mater.*, 2022, **51**, 3092–3100.
- C. Xiao, J. Tian, Q. Chen and M. Hong, *Chem. Sci.*, 2024, **15**, 1570–1610.



Journal Name

ARTICLE

- 36 S. Proding and M. A. Derewinski, *Pet. Chem.*, 2020, **60**, 420–436.
- 37 F. He, J. Zhang, A. Liu and G. Zhu, *E3S Web Conf.*, 2023, **416**, 01001.
- 38 Meili and J. Hai-Long, *CCS Chem.*, 2020, **3**, 2740–2748.
- 39 H.-T. Vu, F. M. Harth and N. Wilde, *Front. Chem.*, 2018, **6**, 1–9.
- 40 F. Cosnier, A. Celzard, G. Furdin, D. Bégin, J. F. Maréché and O. Barrès, *Carbon*, 2005, **43**, 2554–2563.
- 41 Ali, M. A. Hussain, M. T. Haseeb, M. U. Ashraf, M. Farid-ul-Haq, T. Tabassum, G. Muhammad and A. Abbas, *J. Braz. Chem. Soc.*, 2023, **34**, 906–917.
- 42 X. Li, C. Liu, K. Gou, H. Yang, X. Ren and B. Peng, *RSC Adv.*, 2015, **5**, 45420–45425.
- 43 F. Huang and C. Meng, *Int. J. Hydrogen Energy*, 2010, **35**, 6108–6112.
- 44 Q. Fu, F. Xin, X. Yin, Y. Song and Y. Xu, *Int. J. Hydrogen Energy*, 2021, **46**, 22446–22453.
- 45 P. Bian, Y. Wang and T. J. McCarthy, *Macromol. Rapid Commun.*, 2021, **42**, 2000682.
- 46 B. Sebők, M. Schülke, F. Réti and G. Kiss, *Polym. Test.*, 2016, **49**, 66–72.
- 47 J. Liu, L. Ye, S. Wooh, M. Kappl, W. Steffen and H.-J. Butt, *ACS Appl. Mater. Interfaces*, 2019, **11**, 27422–27425.
- 48 X. Yu and C. T. Williams, *Catal. Sci. Technol.*, 2022, **12**, 5765–5794.
- 49 C. Martínez Casillas, M. P. Longinotti, M. M. Bruno, F. Vaca Chávez, R. H. Acosta and H. R. Corti, *J. Phys. Chem. C*, 2018, **122**, 3638–3647.
- 50 K. Schumacher, M. Grün and K. K. Unger, *Microporous Mesoporous Mater.*, 1999, **27**, 201–206.
- 51 T. Kimura and K. Kuroda, in *Comprehensive Inorganic Chemistry II*, ed. J. Reedijk and K. Poeppelmeier, Elsevier, Amsterdam, 2013, pp. 133–150.
- 52 D. Kiadehi and M. Taghizadeh, *Int. J. Hydrogen Energy*, 2018, **43**, 4826–4838.
- 53 Gökaltun, Y. B. Kang, M. L. Yarmush, O. B. Usta and A. Asatekin, *Sci. Rep.*, 2019, **9**, 7377.
- 54 Y. Zhang and R. Wang, *J. Memb. Sci.*, 2013, **443**, 170–180.
- 55 R. Ellerbrock, M. Stein and J. Schaller, *Sci. Rep.*, 2022, **12**, 11708.
- 56 Y. Borodko, J. W. Ager, G. E. Marti, H. Song, K. Niesz and G. A. Somorjai, *J. Phys. Chem. B*, 2005, **109**, 17386–17390.
- 57 Gavran, M. V. Pergal, T. Vicentic, M. Rasljic Rafajilovic, I. A. Pasti, M. V. Boskovic and M. Spasenovic, *Sensors*, 2025, **25**, 5238.
- 58 T. S. Vo, T. S. Nguyen, S.-H. Lee, D. C. T. Vo, D. Kim and K. Kim, *J. Sci. Adv. Mater. Devices*, 2023, **8**, 100554.
- 59 N. J. Pester, M. E. Conrad, K. G. Knauss and D. J. DePaolo, *Geochim. Cosmochim. Acta*, 2018, **242**, 191–212. [View Article Online](#) DOI: 10.1016/j.gca.2018.07.039/D6MA00202A
- 60 Y. Xu, F. Xin, Y. Jiang and X. Yin, *ACS Appl. Mater. Interfaces*, 2021, **13**, 31660–31667.
- 61 X. Fu, J. Hou, C. Chen, J. Li, L. Yue, X. Chen, L. Zhao, G. Ran, X. Xia, Y. Gong, W. Ding, C. Xiao and H. Wang, *J. Hazard. Mater.*, 2019, **380**, 120904.
- 62 S. Hu, L. Xiong, J. Hou, K. Weng, Y. Luo and T. Yang, *Int. J. Hydrogen Energy*, 2010, **35**, 10118–10126.

Open Access Article. Published on 01 Juni 2026. Downloaded on 01.06.2026 17:00:46.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.



Materials Advances Accepted Manuscript

View Article Online
DOI: 10.1039/D6MA00202A

Data availability

The data supporting the findings of this study are available within the article and its Supplementary Information (SI). SI is available. See DOI: <https://doi.org/>

