

REVIEW

[View Article Online](#)
[View Journal](#) | [View Issue](#)Cite this: *J. Mater. Chem. A*, 2023, 11, 2528

Semi-quantitative determination of active sites in heterogeneous catalysts for photo/electrocatalysis

Jing Ren,^a Haoyuan Chi,^{ID}^a Ling Tan,^{ac} Yung-Kang Peng,^{ID}^b Guangchao Li,^d Molly Meng-Jung Li,^d Yufei Zhao^{ID}^{*a} and Xue Duan^a

Catalysis is a widely applied process due to its predominant role in the chemical industry. Developing highly active exposed facets *via* defect engineering is considered to be the most promising strategy for optimizing the electrical and optical properties of catalysts to improve their catalytic activity. Therefore, quantitative determination and calculation of the concentration of defect structures related to the highly exposed active crystal plane provided an efficient route for elucidating the catalytic active sites, and has attracted increasing attention. This work not only summarizes the existing defect characterization methods and the calculation methods of defect concentrations reported in recent years but also proposes a semi-quantitative method based on X-ray absorption fine structure (XAFS) and related methods for the determination and classification of active sites related to the active surface, which can be applied for the semi-quantitative calculation of defect concentrations in widely used metals and metal oxides. In addition, we emphasize the deficiencies of current defect concentration quantitative methods and look forward to the future development of defect characterization methods under working conditions. This review further reveals the structure–activity relationship between the content of active sites and the reaction performance.

Received 19th November 2022
Accepted 8th January 2023

DOI: 10.1039/d2ta09033c

rsc.li/materials-a

1. Introduction

Heterogeneous metal or metal oxide catalysts play a key role in the chemical industry, in which more than 85% of chemical processes involve at least one catalytic step.¹ It is well known that heterogeneous catalysts provide a wide range of active sites such as edges, corners, and facets (*cf.* homogeneous catalysts with well-defined active sites). Therefore, the precise recognition of the active sites of catalysts and the development of high-performance heterogeneous materials are crucial to achieving a green and sustainable society. Early research work reported

^aState Key Laboratory of Chemical Resource Engineering, Beijing University of Chemical Technology, 100029 Beijing, P. R. China. E-mail: zhaoyufei@mail.buct.edu.cn^bDepartment of Chemistry, City University of Hong Kong, Hong Kong SAR, Hong Kong^cState Key Laboratory of Vanadium and Titanium Resources Comprehensive Utilization, ANSTEEL Research Institute of Vanadium & Titanium (Iron & Steel), Chengdu 610031, China^dDepartment of Applied Physics, The Hong Kong Polytechnic University, Hong Kong

Jing Ren is currently studying for her PhD in Beijing University of Chemical Technology under the supervision of Prof. Yufei Zhao at the State Key Laboratory of Chemical Resource Engineering. Her main research interest is photo/electrocatalytic water splitting coupling with organic synthesis.



Haoyuan Chi received his BS degree from China University of Petroleum in 2018 and obtained MS degrees from Beijing University of Chemical Technology in 2021 under the supervision of Prof. Yufei Zhao and Prof. Yufei Song. He is currently a PhD candidate under the guidance of Prof. Xinbin Ma at Tianjin University. His research focuses on preparation and application of layered double hydroxides.

that the performance of catalysts is highly correlated with the elemental composition, and the active center of catalysts is contributed by some elements, which are relatively crude.^{2–4} With the development in the preparation of catalysts and characterization tools, the current focus has been geared to the surface features of catalysts such as corners, edges, and related defect sites, which are believed to determine the observed activity/selectivity.^{5,6} Taking the active crystal surface of the catalyst as an example, some crystal surfaces with high indexes have a higher surface energy because of the existence of more suspended bonds, so they form an open surface structure and exhibit a higher catalytic activity.^{7,8} There is no doubt that defects inevitably exist in all imperfect crystalline materials, and when they appear on the crystal surface, they can significantly regulate the electronic structure of the surface, bringing about changes in their physicochemical properties. Therefore, the

defect structure on the active crystal surface has the structural particularity of the active crystal surface.

A defect is a place in a material where atoms or molecules arranged in perfect periodic are broken or destroyed, which has been regarded to play a prominent role in determining the catalytic activity, and it can be divided into four types according to the size: zero-dimensional point defects (such as vacancies and dopings), one-dimensional linear defects (such as spiral and edge dislocations) mainly existing as edges or corners, two-dimensional planar defects (such as grain boundaries and twin boundaries) that can also be regarded as facets, and three-dimensional volume defects (such as lattice disorders and voids)⁹ (Fig. 1). On the one hand, the formation of defects can further reduce the coordination number of adjacent atoms and provide unsaturated sites for the reactants to adsorb and transform. On the other hand, the existence of defects will



Ling Tan was born in 1993 in Sichuan Province, China. She completed her Bachelor's degree in 2016 at Beijing University of Chemical Technology (BUCT) and obtained her PhD in 2021 at BUCT under the supervision of Prof. Yu-Fei Song. Her research interests mainly focus on the application of 2D nanomaterials in photoreduction of CO₂.



Prof. Yufei Zhao was employed by the State Key Laboratory of Chemical Resource Engineering, Beijing University of Chemical Technology in 2018. His works focus on industrial-scale preparation and application of two-dimensional monolayer materials, efficient utilization of resources, and photocatalytic and electrocatalytic synthesis of high-value fine chemicals. He has published more than 100

SCI papers with more than 18 000 citations (H factor 64), and more than 50 SCI papers as the first/corresponding author, including Chem. Soc. Rev., Adv. Mater., J. Am. Soc. Chem., Angew. Chem., Chem. Eng. Sci. and IECR. He was the "Highly Cited Researcher" selected by Clarivate since 2019–2022.



Dr Peng obtained his PhD degree in 2017 from the University of Oxford in Inorganic Chemistry, for which he served as an Oxford Clarendon scholar as top 3% graduate of 2013 admission year. He is currently an Assistant in Chemistry Department of City University of Hong Kong working on the understanding of surface chemistry for the design and synthesis of hetero(photo) catalysts. He has published over

50 SCI papers in the relevant field and secured fundings more than 4 million HKD as PI.



Prof. Xue Duan, Academician of the Chinese Academy of Sciences, is the Executive Vice-Chair of the Academic Committee of the State Key Laboratory of Chemical Resource Engineering. Over the past 30 years has established a distinctive research program covering "Intercalation Assembly of Layered Materials and Resource Utilization". He has proposed many innovative

concepts such as understanding intercalated structures based on assembly of octahedral units, coupling of catalytic reaction enthalpy and heat transfer, in situ ultrastable mineralization, high-efficiency low-cost green hydrogen, and dual carbon utilization in industrial carbonate hydrorefining. He has been one of the China's most highly cited scientists for many years.



Fig. 1 Quantitative analysis of defects in heterogeneous catalysts for photo/electrocatalysis.

change the electronic structure of the material to promote the interaction between the active site and the reactant intermediates, which regulates the catalytic performance.¹⁰ Thus, the defect engineering of nanomaterials has been widely applied in the field of heterogeneous catalysis.^{11,12} Previous studies have shown that defect engineering can not only affect the physico-chemical properties of heterogeneous materials,^{13,14} but also improve the catalytic performance of photo/electrocatalytic materials.^{15–20} Recently, in order to enhance the efficiency of atom utilization, single-atom catalysts have also come into existence in the research field, and the introduction of defects on the supports of single-atom catalysts can effectively stabilize the single metal atoms and prevent the aggregation of active sites,^{21–23} benefiting the catalysis.

Among the catalysts involved in the chemical production process, heterogeneous metal or metal oxide catalysts have become essential in most refining and petrochemical processes. Metal (hydrogen) oxides represented by layered double hydroxides (LDHs) such as NiO, ZnO, and TiO₂ have attracted extensive research attention due to their excellent photo/electrocatalytic performance. For instance, transition metal (such as Ni, Co and Fe)-containing LDHs are the most promising materials for electrocatalytic oxygen evolution reactions (OERs).^{24,25} The catalytic performance of LDHs can be further improved by introducing defects *via* exfoliation,²⁶ etching,²⁷ and plasma processes.²⁸ With the help of defect engineering, the over-potential of LDHs for OERs has decreased from more than 300 mV to about 190 mV at 10 mA cm^{−2}, as reported by Sun and coworkers.²⁹ Density function theory (DFT) revealed that vacancy-related defects (O vacancies or metal vacancies) can facilitate the adsorption of H₂O³⁰ and, hence, reduce the activation barrier for OERs.³¹ For the photo/electrocatalytic CO₂ reduction reaction, the electronic structure of the catalyst and the adsorption configuration of the intermediates are changed by regulating the defects, which promotes the formation of C₂₊ products.^{32,33} The presence of defects in the electrocatalytic N₂ reduction can also

improve the intrinsic activity and stability of the catalyst.³⁴ In the photolysis water-coupled benzyl alcohol oxidation, the defects can be used as active sites of the reaction and also effectively inhibit the photogenerated electron–hole recombination.³⁵ Therefore, defect engineering is an efficient strategy to prepare catalysts in improving photo/electrocatalysis. In view of these encouraging results, researchers began to study the defects in more depth and detail. However, how to determine the catalytic active site qualitatively or semi-quantitatively is still a challenge at this stage. Therefore, it is crucial to develop a route to identify the key active site of the target catalysts, particularly in *in situ* or *operando* conditions.^{36–39}

At present, defects can be well characterized by electron microscopy and spectroscopy analyses such as transmission electron microscopy (TEM), aberration-corrected high-angle annular dark-field scanning transmission electron microscopy (HAADF-STEM), X-ray absorption fine structure (XAFS), electron spin resonance (ESR), positron annihilation spectroscopy (PAS), nuclear magnetic resonance (NMR), X-ray photoelectron spectroscopy (XPS), and photoluminescence spectroscopy (PL). Some peers have summarized the synthesis and characterization methods of defects.¹² The catalytic performance as well as the selectivity of a given reaction is known to change with the number/type of defects. Note that the appearance of certain defects generates positive/negative effects. For example, our group found that the selectivity of methane increases and that of H₂ decreases with the increase in defects in NiAl-LDH⁴⁰ from photocatalytic CO₂ reduction. Furthermore, Zhao and co-workers investigated the concentration ratio between bulk and surface defects in TiO₂ and concluded that bulk defects will lead to the recombination of carriers, resulting in a decreased photocatalytic activity.⁴¹ Therefore, understanding the relationship between defect concentration and performance can help us rationally design smart catalysts.

Herein, we summarize the current representative work of constructing defects on the exposed active facet to improve photo/electrocatalytic activity, and quantification of the defects *via* various characterizations such as TEM, XAFS, NMR, PAS, ESR, XPS, PL, and FT-IR, as shown in Fig. 1. On the basis of previous works on quantifying defects, we also propose a semi-quantitative defect concentration method based on highly active facets using XAFS and related methods, and provide a description on the location, type and concentration of defect sites. By using this calculation, we can obtain the concentration information of defects in the target facet, which is helpful to accurately quantify the role of defect sites in the reaction process using *in situ* technology and to design efficient catalysts *via* defect engineering in the future.

2. Advanced methods for determining and semi-quantifying defects

2.1. Electron microscopy

The electron microscope is an indispensable microscopic tool in the field of materials science, which can clearly and

intuitively show the morphology of the nanomaterials at atomic-level resolution. With the use of TEM, scanning tunneling microscopy (STM), and HAADF-STEM, we can unambiguously identify the thickness, size, exposed facets, surface defects, *etc.*, of the nanomaterials. For example, long-range and local structural details of electrodes and solid electrolyte materials were revealed using advanced TEM techniques, which provides a new view on the energy conversion and storage.⁴² Moreover, the morphology, multiphase distribution, and even the atomic arrangement around the structural defect regions of nanostructured materials can also be distinguished from (S)TEM images. Recently, Wang and co-workers have covered the visualized observation of the morphology of SnS₂, and the presence of defect regions in the structure.⁴³ As shown in Fig. 2A, the lattice spacing of pristine SnS₂ is about 0.587 nm, which corresponds well to the (001) facet of SnS₂ (0.585 nm). While the discontinuous lattice fringes can be clearly observed in the HRTEM image of SnS₂ featuring Al doping (Fig. 2B), it can be inferred that the fractional crooked fringes observed in the fuzzy region may donate the existence of defects. These consequences represent that Al doping successfully introduced defects in the (001) crystal plane of SnS₂. By observing the HRTEM images, it can also be clearly found that β -Ni(OH)₂ ultra-thin nanosheets are distributed with nanopores of size 3–4 nm, further indicating the wide existence of defects in some traditional materials.⁴⁴ To gain insights into the defects of the material, Xie's group used HAADF-STEM to reveal the microstructure of Bi₂O₃ with rich oxygen vacancies.⁴⁵ The apparent lattice disorder in Fig. 2C verified the existence of a metal coordination unsaturated structure in the material. Furthermore, the fast-scanning Aarhus STM and time-lapsed sequential STM images allow us to detect the presence of defects and monitor the diffusion behavior of some small molecules such as H₂O^{46,47} and O₂.^{37,38} For instance, as shown in Fig. 2D–F, Besenbacher's team successfully tracked the diffusion behavior

of a single O₂ molecule on O vacancies of TiO₂(110) by STM technology.³⁸ They observed that the diffusion of O₂ molecules only along the (001) direction and the O₂ hopping rates are related to the content of O vacancies on the surface: the oxygen jumping rate increases with the increase in the content of O vacancies at an appropriate temperature. Using STEM, Dou's team revealed that the O vacancies on the TiO₂(110) surface promote HER processes in alkaline media.⁴⁶ The O vacancy concentration decreased with the increase in surface depth (Fig. 2D–F). In the HER process, H₂O molecules preferentially adsorbed onto the O vacancy surface, and one O vacancy could induce two Ti³⁺ (Fig. 2G and H). The O vacancies and Ti³⁺ ions in the surface region determine the conductivity and the number of electrocatalytic active sites of TiO₂.

As the most intuitive and clear evidence, microscopy plays an indispensable role in estimating the presence and location of defects in heterogeneous catalysts. In last several years, the development of *in situ* electron microscopy has also led to its application in many fields such as ion migration in lithium-ion batteries,^{48,49} the interaction between metal nanoparticles and oxide support under redox conditions,^{39,50,51} and the structural transformation of metals in the gas phase⁵² or during heating up.⁵³ Even though electron microscopy cannot accurately quantify the concentration of defects at present, it is still making an important contribution to the study of the transition process of defects under working conditions.

2.2. X-ray absorption fine structure (XAFS)

X-ray absorption fine structure (XAFS) spectrum is one of the most powerful tools for determining the local structures. Therefore, *via* the X-ray absorption fine structure (EXAFS) analysis, the following information such as the coordination number, bond length, defect concentration, and disorder degree of the coordination atoms around the central absorption atom can be accurately obtained. Compared with EXAFS, X-ray absorption near edge structure (XANES) is more ingenious to spatial structure information and can obtain valency and symmetry information qualitatively and effectively. *Via* combination with the AFM and TEM information, the defect concentration and the density of the defect can be accurately obtained as follows:

Taking layered double hydroxides (LDHs), layered materials consisting of brucite-like positively charged laminates, and negatively charged interlaminal anions and water molecules,⁵⁶ as examples, our group synthesized the defect-containing ultrathin LDH photocatalyst for photocatalytic phenol oxidation. We used XAFS technology to study the local structure of defective NiFe-LDH synthesized by a co-precipitation method, as shown in Fig. 3A.⁵⁴ As can be seen from the *R*-space of Ni shown in Fig. 3B, the coordination number of the first shell (Ni–O) and the second shell (Ni–Ni/Fe) of NiFe-LDH nanosheets ($N_{\text{Ni–O}} = 5.3$, $N_{\text{Ni–Ni/Fe}} = 5.4$) are much lower than that of the NiFe-LDH bulk counterpart ($N_{\text{Ni–O}} = 6$, $N_{\text{Ni–Ni/Fe}} = 6$). The same result can be also observed in Fe K-edge EXAFS (Fig. 3C), further indicating the presence of O, Ni and Fe vacancies (V_{OH} , V_{Ni} , and V_{Fe}) in NiFe-LDH nanosheets. However, the quantification of



Fig. 2 HRTEM images of (A) pristine SnS₂ and (B) SnS₂ featuring Al doping⁴³ copyright © 2021 Elsevier B.V. (C) HAADF-STEM images of V_O-rich-Bi₂O₃ nanosheets, the scale bar is 2 nm.⁴⁵ Copyright © 2019, Springer Nature Limited. STEM image of cross-sectional TiO₂(110) single crystal (D) and large region (E). (F) Concentration of O vacancies increased from inner to surface regions. (G) STM image of the TiO₂ surface in the empty state. (H) STM image of the same region of (G), but in the filled state⁴⁶ copyright © 2018 American Chemical Society.



Fig. 3 (A) Structural model of NiFe-LDH nanosheets and NiFe-LDH bulk; R space of the (B) Ni and (C) Fe K-edge EXAFS spectra.⁵⁴ Copyright © 2020 Royal Society of Chemistry. (D) R space of Ni K-edge EXAFS spectra. (E) Schematic illustration of the basic unit cell of monolayer NiAl-LDH.⁵⁵ Copyright © 2019 Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim.

defects and the provision of their location on the LDH/nanoparticles are both unclear.

In order to further explore the relationship between the defect concentration and performance, our group prepared bulk, few-layer, and monolayer NiAl-LDH nanosheets (denoted as b-NiAl-LDH, f-NiAl-LDH, and m-NiAl-LDH, respectively) for photoreduction of CO₂.⁵⁵ The coordination numbers of Ni and O decreased with the decrease in the thickness of NiAl-LDH, indicating that the Ni and O vacancies increased sequentially, and the selectivity of the target product CH₄ also increased sequentially (Fig. 3D). It is easy to find that the selectivity of target product CH₄ and the quantity of Ni vacancies and O vacancies are closely related.

According to the coordination number information obtained by XAFS and the detail of the basic unit cells, a method for quantifying defect concentration was summarized. Taking m-NiAl-LDH as an example (Fig. 3E), the surface area of one LDH cell can be calculated as $1.2 \text{ nm} \times 1.2 \text{ nm} \times \sin 60^\circ = 1.247 \text{ nm}^2$. The cell parameter c of LDHs is related to interlayer anions, and different interlayer anions lead to different layer thicknesses and eventually lead to differences in c ; therefore, the volume of the LDHs can be obtained as follows: surface area of the cell \times thickness (nm), where the thickness is measured by atomic force microscopy (AFM) results (1 nm). The corresponding oxygen number in this m-NiAl-LDH model is referred to as 32, and the metal (Ni and Al) atom number is 16. As obtained from the EXAFS results of m-NiAl-LDH, the corresponding coordination number of the first Ni–O shell is 5.5,

compared with the pure LDH with a coordination number of 6.0, the ratio of the defect concentration of the Ni–O shell in m-NiAl-LDH is proposed to be around $(5.5 - 6)/6 = 8.3\%$. Therefore, in the whole model, the defect intensity of O vacancies can be inferred as follows: oxygen vacancies density (nm^{-3}) = ratio of the defect concentration \times the total oxygen number in the model per $\text{nm}^3 = 8.3\% \times 32 / (1.247 \text{ nm}^2 \times 1 \text{ nm}) = 2.14 \text{ nm}^{-3}$. The above-mentioned equation can also be extended to calculate the metal vacancies density, and the metal vacancies density (nm^{-3}) in m-NiAl-LDH can be obtained as: the ratio of the defect concentration \times the total metal number in the model per $\text{nm}^3 = (6.0 - 5.0)/6.0 \times 16 / (1.247 \text{ nm}^2 \times 1 \text{ nm}) = 2.14 \text{ nm}^{-3}$. Accordingly, the defect density of O and Ni vacancies in f-NiAl-LDH was calculated to be 1.80 nm^{-3} and 1.20 nm^{-3} , respectively. Defect density provides a guideline for regulating the selectivity/activity of catalytic reactions and exploring the corresponding structure–activity relationship. In addition, our proposed method can also be applied to other LDH materials such as CoFe-LDH,^{57–59} ZnAl-LDH,⁶⁰ and NiFe-LDH.^{61,62} The concentrations of oxygen defects and metal defects for other LDHs in recent reports were also calculated, and the results are presented in Table 1. It is worth noting that the concentration of oxygen defects and metal defects ranges from 0.05 to 10.69 nm^{-3} , and is closely related to the types of metal elements that compose the LDH laminate. Then, a defect location site description can be defined as follows: material-defect type-active exposed facet-concentration, like NiAl-LDH- $V_{\text{O}(001)}$ -2.14 nm^{-3} . This semi-quantitative calculation method of defect concentration provides guidance for accurate defect engineering design to achieve better performance control.

The above-mentioned calculation can also be applicable to other catalysts such as ZnO, NiO, and TiO₂. Chergui and co-workers quantitatively analyzed the oxygen and Zn vacancies for colloidal ZnO nanoparticles with different sizes.⁶³ With the help of EXAFS, the peak intensity of the first shell (Zn–O) of the three samples with different sizes is similar to the R space spectrum, indicating that the number of their oxygen vacancies is comparable. However, the relative intensity of the second shell (Zn–Zn) peak decreases with the size of ZnO, indicating that the number of Zn vacancies increases with the decrease in ZnO transverse size. Besides, Passerini and co-workers also performed EXAFS to obtain the quantitative structural information of Fe/Co-doped ZnO.⁶⁴ They found that Fe doping leads to more cation and oxygen vacancies in ZnO than Co-doped ZnO. With the introduction of O and Zn defects, the optical properties and ferromagnetism of ZnO materials were improved.⁶⁵ Some papers also give the fitting results of EXAFS, and then combined with the crystal cell information of ZnO, we can calculate the defect density of Zn and O vacancies accordingly. The volume of the ZnO cell can be obtained as follows: $a \times b \times c \times \sin 120^\circ = 0.324927 \text{ nm} \times 0.324927 \text{ nm} \times 0.520544 \text{ nm} \times \sin 120^\circ = 0.0476 \text{ nm}^3$. The number of O and Zn atoms in the ZnO unit model is 2, and the coordination number of oxygen and Zn is 4 and 12, respectively. As obtained from the EXAFS results of ZnO, the defect density of the Zn–O shell in ZnO was calculated to be around $(4 - N_{\text{O}})/4 \times 2/0.0476 \text{ nm}^{-3}$ and the defect density of the Zn–Zn shell in ZnO is thus around

Table 1 Calculation of oxygen defect and metal defect density in LDH materials

No.	Sample	Thickness (nm)	N_{M-O}	V_O (nm ⁻³)	N_{M-M}	V_M (nm ⁻³)	Reference
1	Bulk NiAl-LDH	27	$N_{Ni-O} = 6.0$	$V_{O(001)} = 0$	$N_{Ni-M} = 6.0$	$V_{M(001)} = 0$	55
	Fewlayer NiAl-LDH	5	$N_{Ni-O} = 5.7$	$V_{O(001)} = 0.26$	$N_{Ni-M} = 5.6$	$V_{M(001)} = 0.17$	
	Monolayer NiAl-LDH	1	$N_{Ni-O} = 5.5$	$V_{O(001)} = 2.14$	$N_{Ni-M} = 5.0$	$V_{M(001)} = 2.14$	
2	CoFe-LDH	4.5	$N_{Fe-O} = 6.0$	$V_{O(001)} = 0$	$N_{Fe-M} = 5.7$	$V_{M(001)} = 0.14$	57
	NiCoFe-LDH	3.3	$N_{Fe-O} = 5.2$	$V_{O(001)} = 1.04$	$N_{Fe-M} = 4.1$	$V_{M(001)} = 1.23$	
3	Bulk NiFe-LDH	20	$N_{Fe-O} = 6.0$	$V_{O(001)} = 0$	$N_{Fe-Ni} = 6.0$	$V_{M(001)} = 0$	61
	Monolayer NiFe-LDH	1	$N_{Fe-O} = 5.9$	$V_{O(001)} = 0.43$	$N_{Fe-Ni} = 5.8$	$V_{M(001)} = 0.43$	
	Ultrafine NiFe-LDH	0.6	$N_{Fe-O} = 5.8$	$V_{O(001)} = 1.43$	$N_{Fe-Ni} = 5.5$	$V_{M(001)} = 1.78$	
4	Pristine CoFe-LDH	27.5	$N_{Co-O} = 4.9$	$V_{O(001)} = 0.17$	$N_{Co-M} = 5.3$	$V_{M(001)} = 0.05$	58
	H ₂ O-plasma exfoliated-CoFe LDH	1.54	$N_{Co-O} = 4.7$	$V_{O(001)} = 3.61$	$N_{Co-M} = 4.4$	$V_{M(001)} = 2.22$	
5	Bulk CoFe-LDH	20.6	$N_{Fe-O} = 4.7$	$V_{O(001)} = 0.27$	$N_{Fe-M} = 4.4$	$V_{M(001)} = 0.17$	59
	Ultrathin CoFe-LDH	0.6	$N_{Fe-O} = 4.5$	$V_{O(001)} = 10.69$	$N_{Fe-M} = 3.6$	$V_{M(001)} = 8.55$	
6	Monolayer NiFe-LDH	0.8	$N_{Fe-O} = 5.9$	$V_{O(001)} = 0.53$	$N_{Fe-M} = 5.7$	$V_{M(001)} = 0.80$	62
	Porous monolayer NiFe-LDH	0.8	$N_{Fe-O} = 5.7$	$V_{O(001)} = 1.60$	$N_{Fe-M} = 5.1$	$V_{M(001)} = 2.41$	

$(12 - N_{Zn})/12 \times 2/0.0476 \text{ nm}^{-3}$. The calculated results of the ZnO defect density are listed in Table 2.

The study of O and Ni defects in NiO materials also makes an important contribution to the interpretation of the structure–activity relationship. Langell and co-workers used XAFS to study the coordination environment of bulk, 25 nm, and 5 nm NiO nanomaterials.⁶⁶ Gutiérrez and co-workers revealed from the XAFS results that the resistivity of NiO films is intimately in connection with the Ni defects.⁶⁷ Therefore, the quantification of defect density is instructive for NiO defect engineering. By fitting the *R* space, the defect densities of O vacancies and Ni vacancies can also be calculated from the coordination number results obtained by XAFS. The volume of the NiO cell can be obtained as follows: $a \times b \times c = 0.41684 \text{ nm} \times 0.41684 \text{ nm} \times$

$0.41684 \text{ nm} = 0.0724 \text{ nm}^3$. The number of O and Ni atoms in the NiO unit model is 4, and the coordination number of O and Ni is 6 and 12, respectively. As obtained from the EXAFS results of NiO, the defect density of the Ni–O shell in NiO was calculated to be around $(6 - N_O)/6 \times 4/0.0724 \text{ nm}^{-3}$ and the defect density of the Ni–Ni shell in NiO is around $(12 - N_{Ni})/12 \times 4/0.0724 \text{ nm}^{-3}$. *Via* calcination of the NiTi-LDH monolayer precursor, the (110) facet-exposed NiO can be obtained.⁶⁸ Together with the results of AFM, TEM, and XAFS, the synthesized NiO(110) facet contains abundant O and Ni defects, which promote water adsorption and later charge transfer process in the OER. Our group also successfully synthesized NiO enclosed by the (110) facet using a NiAl-LDH precursor.⁶⁹ *Via* the calculation of defect concentration in Table 2, it was found that the photocatalytic

Table 2 Calculation of oxygen defect and metal defect density in ZnO and NiO

No.	Sample	N_{M-O}	V_O (nm ⁻³)	N_{M-M}	V_M (nm ⁻³)	Reference
1	Standard ZnO	$N_{Zn-O} = 4$	$V_O = 0$	$N_{Zn-Zn} = 12$	$V_{Zn} = 0$	65
	ZnO doping Ni 5%	$N_{Zn-O} = 3.3$	$V_O = 7.35$	$N_{Zn-Zn} = 11.5$	$V_{Zn} = 1.75$	
	ZnO doping Ni 12.5%	$N_{Zn-O} = 2.8$	$V_O = 12.61$	$N_{Zn-Zn} = 10.9$	$V_{Zn} = 3.85$	
2	ZnO aliquot 1	—	—	$N_{Zn-Zn} = 6.7$	$V_{Zn} = 18.56$	79
	ZnO aliquot 2	—	—	$N_{Zn-Zn} = 8.7$	$V_{Zn} = 11.55$	
	ZnO aliquot 3	—	—	$N_{Zn-Zn} = 11.5$	$V_{Zn} = 1.75$	
	Standard NiO	$N_{Ni-O} = 6$	$V_O = 0$	$N_{Ni-Ni} = 12$	$V_{Ni} = 0$	
3	NiO from Ni(CH ₃ COO) ₂	$N_{Ni-O} = 5.7$	$V_O = 2.76$	$N_{Ni-Ni} = 10.7$	$V_{Ni} = 5.99$	72
	NiO from Ni(acac) ₂	$N_{Ni-O} = 5.5$	$V_O = 4.60$	$N_{Ni-Ni} = 7.5$	$V_{Ni} = 20.72$	
	NiO from Ni(acac) ₂ without TOPO	$N_{Ni-O} = 6$	$V_O = 0$	$N_{Ni-Ni} = 10.3$	$V_{Ni} = 7.83$	
4	NiAl-275	$N_{Ni-O} = 5.5$	$V_{O(110)} = 4.60$	$N_{Ni-M} = 7.2$	$V_{M(110)} = 22.10$	69
	NiAl-600	$N_{Ni-O} = 5.8$	$V_{O(110)} = 1.84$	$N_{Ni-M} = 10.1$	$V_{M(110)} = 8.75$	
	NiAl-800	$N_{Ni-O} = 6.0$	$V_{O(110)} = 0$	$N_{Ni-M} = 10.7$	$V_{M(110)} = 5.99$	
5	NiO/SiO ₂	$N_{Ni-O} = 6.0$	$V_O = 0$	$N_{Ni-Ni} = 11.6$	$V_{Ni} = 1.84$	73
	NiO/Ti-anat	$N_{Ni-O} = 5.3$	$V_O = 6.45$	$N_{Ni-Ni} = 10.9$	$V_{Ni} = 5.06$	
	NiO/Ti-P25	$N_{Ni-O} = 5.2$	$V_O = 7.37$	$N_{Ni-Ni} = 10.4$	$V_{Ni} = 7.37$	
6	Fe-doped NiO _x nanotubes	$N_{Ni-O} = 5.2$	$V_O = 7.37$	$N_{Ni-Ni} = 10.2$	$V_{Ni} = 8.29$	74
7	NiO-10% oxygen	$N_{Ni-O} = 6$	$V_O = 0$	$N_{Ni-Ni} = 11.8$	$V_{Ni} = 0.92$	75
	NiO-40% oxygen	$N_{Ni-O} = 6$	$V_O = 0$	$N_{Ni-Ni} = 11.4$	$V_{Ni} = 2.76$	
	NiO-70% oxygen	$N_{Ni-O} = 6$	$V_O = 0$	$N_{Ni-Ni} = 11$	$V_{Ni} = 4.60$	
8	Bulk NiO	$N_{Ni-O} = 6$	$V_O = 0$	$N_{Ni-Ni} = 12$	$V_{Ni} = 0$	76
	25 nm NiO	$N_{Ni-O} = 5.5$	$V_O = 4.60$	$N_{Ni-Ni} = 10.6$	$V_{Ni} = 6.45$	
	5 nm NiO	$N_{Ni-O} = 5.4$	$V_O = 5.52$	$N_{Ni-Ni} = 10.4$	$V_{Ni} = 7.34$	
9	Mono-NiTi-MMO	$N_{Ni-O} = 5.7$	$V_{O(110)} = 2.76$	$N_{Ni-Ni} = 7.7$	$V_{Ni(110)} = 19.80$	68

selectivity of CO₂ reduction to CH₄ increased with the increase in metal defect concentration in NiO. Quantifying defects in NiO can provide a new perspective for exploring the relationship between the structure and the performance.

Based on this method, we can quantitatively calculate the number of metal defects and oxygen defects per cubic nanometer of metal (hydrogen) oxides. The defect concentrations of the most widely reported materials such as LDHs, NiO, and ZnO for photo/electrocatalysis in recent years were thus calculated, as shown in Fig. 4. It is not difficult to find that the concentration of defects affects the catalytic performance of the material. The proposed method solves the problem of defect quantification to some extent and helps understand the structure–activity relationship between defect concentration and catalytic performance. With the development and application of *in situ* XAFS, the real atomic and electronic structures of catalysts can be

monitored under working conditions.^{77,78} It is promising that *in situ* techniques can be used to reveal the active sites of catalysts and accurately quantify the concentration of defects.

However, this quantitative method is limited to XAFS results, which only show the changes in the overall material coordination environment, and it is difficult to distinguish which defects cause the changes. Therefore, the defect density calculated by this method cannot represent the density of a certain type of defect. In addition, the coexistence of multiple metal oxides and amorphous phases also set up obstacles for the selection of appropriate cell elements, which hinders the accurate calculation of defect density, and still needs to be explored in the future.

2.3. Nuclear magnetic resonance (NMR)

NMR is a mighty characterization technique for materials containing a large number of spin-active nuclei. By this technique, we can acquire information about the regional structure of materials, like the micro-arrangement of cations. It also makes up for some light metal elements such as Mg and Al, which are difficult to characterize by XAFS to a certain extent. Taking ²⁵Mg-NMR as an example, although the development has been challenged by low sensitivity due to low gyromagnetic ratio and natural abundance, combined with large quadrupole moment of isotopes, they have gained much research interest in Mg-containing LDH structures. By studying the ¹H and ²⁵Mg NMR spectra of MgAl-LDH with different Al contents, Grey's team first revealed the arrangement order of cations in the material.⁸⁰ When the ratio of Mg to Al was 2:1 with a “honeycomb” ordering, the arrangement of Mg and Al was perfectly ordered, while in the case of low Al contents, cations were randomly arranged in the case of no Al³⁺–Al³⁺ close contacts. Inspired by this work, Massiot's group used ¹H and ²⁷Al NMR spectroscopy to identify and quantify the defect in cation arrangement of MgAl-LDH.⁸¹ The cation distribution of MgAl-LDH was predicted by ¹H solid-state NMR technology combined with DFT theoretical calculations, as shown in Fig. 5A, and the optimized model of LDH intercalated with nitrate as shown in Fig. 5B was proposed. The ascendant peak of 3.8 ppm in Fig. 5A was identified as the Mg₂AlOH species, while the shoulder peak at 4.6 ppm corresponded to interlaminar or adsorbed water. The little peak at 1.6 ppm was contributed by the Mg₃OH. The defect concentrations of different Mg to Al content ratios can be estimated according to the fitting and integration of ¹H NMR spectra, as shown in Fig. 5C, and the specific calculation formula is as follows:⁸¹

Al defects:

$$x_{M^{3+}}^{\text{defects}} = \frac{n_{M^{3+}}^{\text{defects}}}{n_{M^{3+}}} = \left(\frac{n_{M^{3+}}^{\text{defects}}}{n_{OH}^{\text{defects}}} \right) \left(\frac{x_{OH}^{\text{defects}}}{x} \right) \left[\frac{n_{OH}}{n(M^{2+} + M^{3+})} \right]$$

Mg defects:

$$x_{M^{2+}}^{\text{defects}} = \frac{n_{M^{2+}}^{\text{defects}}}{n_{M^{2+}}} = \left(\frac{n_{M^{2+}}^{\text{defects}}}{n_{OH}^{\text{defects}}} \right) \left(\frac{x_{OH}^{\text{defects}}}{1-x} \right) \left[\frac{n_{OH}}{n(M^{2+} + M^{3+})} \right]$$

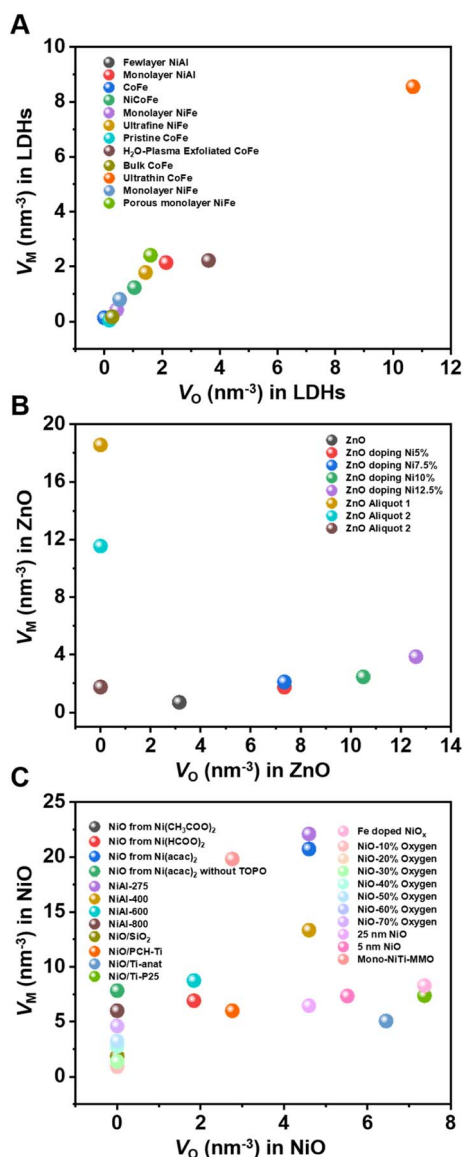


Fig. 4 Oxygen defect and metal defect density in (A) LDHs; (B) NiO; and (C) ZnO.^{55,57–59,61,62,68–76}



Zn₃C (I and II) and TMP-proton (III and IV) species were further confirmed by DFT calculations (Fig. 6B). Since one can obtain the amount of these TMP adsorbed sites (I to IV) from the area of their $\delta^{31}\text{P}$ signal, not only the distribution but also the concentration of Zn₃C, V_o, and hydroxyl groups can be provided for each sample (Fig. 6C). This allows for a reliable correlation of surface sites to their photocatalytic activities in both qualitative and quantitative manners. Therefore, the photocatalytic oxidation of surface hydroxyl groups to OH radicals was revealed.⁸⁹

Recently, the same group also studied the surface effect of CeO₂ shapes in two enzymatic reactions (Fig. 7A).^{92,93} A CeO₂ cube terminated by the (100) facet was found to display high activity in H₂O₂ conversion,⁹² while it is nearly inactive in dephosphorylation reactions.⁹³ Interestingly, CeO₂ octahedron with the (111) exposure shows a total reverse trend in both reactions. The chemical state of surface Ce revealed by TMP-³¹P NMR suggested that Ce has stronger Lewis acidity on the (111) facet of the octahedron (more Ce⁴⁺ like) while weaker Lewis acidity on the (100) facet of the cube (more Ce³⁺ like) (Fig. 7C).⁹⁴ One can thus easily achieve *ca.* 1000% (for cube in H₂O₂ conversion) and 4500% (for octahedron in dephosphorylation) increase for pristine CeO₂ if its terminal facet is wisely selected for a given reaction. In addition to the facet effect, the electronic effect of “surfactant” (*e.g.*, fluorine) imposed on surface five-coordinated Ti (Ti_{5c}) was also revealed by TMP-³¹P NMR

(Fig. 7B).⁹⁰ As HF, a structure-directing agent can efficiently stabilize the high-energy (001) facet of anatase TiO₂ (*cf.* thermodynamic stable (101)), and the percentage of exposed (001)/(101) facet can thus be tuned by added HF. TMP-³¹P NMR spectra revealed that the 0HF sample has ~90% of Ti_{5c} on the most stable (101) facet (−36 ppm) and less than 10% of Ti_{5c} on the high-energy (001) facet with higher acidity (−29 ppm). While for 2HF and 6HF, the presence of surface F observably shifts the chemical state of Ti_{5c} on the (101) and (001) facets to −31 and −22.5 ppm and produces extra surface features such as acidic proton (−2.6 ppm, TMPH⁺) and oxygen vacancy (−42.5 ppm). This technique also demonstrated its power in monitoring the change in Ti_{5c} chemical state in the course of F removal (NaOH wash) and later sulfate modification (Fig. 7D).⁹¹ As TiO₂ surfaces can be comprehensively mapped, the key Ti_{5c} site dictating TiO₂ facet activity in Pechmann condensation,⁹¹ dephosphorylation reaction,⁹⁵ photocatalytic hydrogen evolution,⁹⁶ and water splitting⁹⁷ was thus revealed.

Moreover, TMP-³¹P NMR can be used to identify different Al species, Zheng's group used DFT calculations in combination with ³¹P NMR experiments, where TMP was the probe molecule to conduct a comprehensive study on the existence of tri-coordinated EFAL-Al³⁺ species in the zeolitic catalysts, which is usually undetectable by conventional one- and two-dimensional ¹H and/or ²⁷Al solid-state NMR.⁹⁸ In addition to TMP, TMPO as a ³¹P probe molecule is preferentially attached to acid sites on solid catalysts, thus providing qualitative and quantitative information on Brønsted and Lewis acid sites.⁸⁵ The development of NMR and the expansion of various probe molecules has enabled the quantitative study of the types, densities and intensities of various sites,^{99,100} which is a powerful means to identify the surface characteristics of catalysts.

The combination of NMR with other complementary techniques has allowed researchers to investigate surface active sites and their connection to structural flexibility and defect formation. For instance, Tsang's group used Raman, XPS, XAFS, and ⁹³Nb NMR to gain new insights into the structure-acidity correlations of nanosize niobium oxides with non-stoichiometric structural variety.¹⁰¹ Besides, combining NMR with *in situ* techniques can provide valuable information about dynamic changes in active sites under catalyst working conditions. For example, Li and co-workers used solid-state NMR, *in situ* synchrotron X-ray powder diffraction, and infrared spectroscopy to show that traditional Brønsted acid sites (Si–O(H)–Al) on silicoaluminophosphate zeolites can be transformed into Frustrated Lewis Pairs *via* breaking the Al–O bond in the framework upon adsorption of polar small molecules.¹⁰² Similar active site transformations can also be promoted at elevated temperatures.¹⁰³ These findings highlight the importance of using combined characterizations and *in situ* techniques for active site identification.



Fig. 7 (A) TEM images of CeO₂ terminated with the (111), (110), and (100) facets, respectively, and schematic illustration of H₂O₂ conversion (left) and dephosphorylation reaction (right). (B) TEM and TMP-³¹P NMR spectra of different TiO₂ facets.⁹⁰ Copyright © 2017 Springer Nature Limited. (C) TMP-³¹P NMR spectra of CeO₂ shapes. (D) TMP-³¹P NMR spectra of NaOH- and sulfate-modified samples.⁹¹ Copyright © 2018 Royal Society of Chemistry.

2.4. Positron annihilation spectroscopy (PAS)

PAS is favored by researchers because it can non-destructively study the internal microstructure and defect state of species. Researchers often employ coincidence Doppler broadening

(CDB) and positron lifetime of positron annihilation spectroscopy (PAS) to study the defective structure of heterogeneous materials. In the CDB spectrum, the low electron density at the vacancy defect leads to a decrease in the average momentum of the annihilated electron and a narrow spectral line, while the positron lifetime in the PAS test corresponds to defects of different sizes.

PAS technology can be used to accurately locate defect types (like isolated or double or triple defects) that cannot be clearly identified by XAFS technique. Xie's team successfully prepared ultrathin BiOCl nanosheets that nearly exposed the active (001) facet, and used PAS technology to reveal that the main component of the defect changed from single-defect $V_{\text{Bi}}^{\bullet\bullet}$ to triple vacancy-associated defect $V_{\text{Bi}}^{\bullet\bullet}V_{\text{O}}^{\bullet\bullet}V_{\text{Bi}}^{\bullet\bullet}$ as the thickness of the nanosheets decreased to the atomic scale.¹⁰⁴ As shown in Fig. 8A and D, both the ultrathin BiOCl nanosheets and nanoplates yield four lifetime components in the PAS spectrum. The two longer lifetimes (τ_3 , 550–590 ps, and τ_4 , 2.2–2.5 ns) correspond to large defect clusters and positron annihilation between material interfaces, respectively. Based on the theoretically calculated positron lifetime (Fig. 8E), the shortest lifetime (τ_1 , about 250 ps) observed in the PAS spectrum can correspond to positron annihilation trapped in a single isolated bismuth vacancy (Fig. 8B), while another lifetime (τ_2 , about 325 ps) was attributed to $V_{\text{Bi}}^{\bullet\bullet}V_{\text{O}}^{\bullet\bullet}V_{\text{Bi}}^{\bullet\bullet}$ associated with Bi^{3+} -oxygen vacancies (Fig. 8C). Obviously, the Bi^{3+} -oxygen triple vacancies mainly exist in the ultrathin nanosheets, while $V_{\text{Bi}}^{\bullet\bullet}$ mainly exists in the

nanoplates by analyzing their PAS results. The combination of PAS technology with XAFS and other representation technologies can accurately determine the type of defects and calculate the density of the defects semi-quantitatively, thus giving a deeper understanding of the defects.

Recently, some researchers have found that bulk vacancy defects and surface vacancy defects have discrepant effects on catalysis. Zhao and co-workers explored for the first time the relationship between bulk/surface defects in TiO_2 and the corresponding photocatalytic efficiency.⁴¹ The different concentration ratio of bulk defects to surface defects in anatase TiO_2 was realized by vapor-induced hydrothermal hydrolysis of titanium butoxide at 120 °C, 180 °C (denoted as TiO_2 -120, TiO_2 -180) and calcination of TiO_2 -180 at 480 °C (denoted as TiO_2 -480). The intensity (I) of the positron lifetime reflects their relative concentration. The ratio of I_1 to I_2 (I_1/I_2) performed by PAS represents the ratio of the concentration of volume defects to surface defects. I_1/I_2 decreases from 1.01 for TiO_2 -120 to 0.45 for TiO_2 -180, manifesting a decline of the concentration ratio of bulk-to-surface defects. TiO_2 -120 with the highest ratio shows the lowest photocurrent response, which is because of the recombination of charge carriers in the bulk defects. This phenomenon may attribute to interfacial defects from bulk defects in TiO_2 , which is confirmed by the positron lifetime that τ_1 for TiO_2 is larger than that for TiO_2 -120. This work indicated that controlling the content ratio of bulk-to-surface defects is highly essential for photocatalysis. It is well known that catalysis happens on the surface, the PAS also provides information about the defects on the surface, while XAFS and NMR always provide a statistical result no matter from the surface or bulk structure.

The defect structure information of metal catalysts can also be obtained by PAS. Wei and co-workers reported a Ru-Ni catalyst (denoted as $\text{Ru}_{0.8}\text{-Ni/H-Al}_2\text{O}_3$) that anchored Ru clusters to the defect sites of Ni nanoparticles (denoted as $\text{Ni/H-Al}_2\text{O}_3$) prepared by topotactic reduction of the NiAl-LDH precursor.¹⁰⁵ The materials obtained from $\text{Ni/H-Al}_2\text{O}_3$ annealed at 500 °C and 550 °C were denoted as $\text{Ni}_{\text{A500}}/\text{H-Al}_2\text{O}_3$ and $\text{Ni}_{\text{A550}}/\text{H-Al}_2\text{O}_3$, respectively. Based on the CDB spectra of the samples distributed along a straight line obtained by PAS, it can be inferred that these samples mainly have Ni defects. After anchoring Ru clusters, the increase in τ_2 from 381.5 ps to 424.8 ps could be attributed to the appearance of Ru-Ni interface, improving the electron density on Ni vacancy clusters. A similar I_2/I_1 ratio observed between $\text{Ni/H-Al}_2\text{O}_3$ (1.40) and $\text{Ru}_{0.8}\text{-Ni/H-Al}_2\text{O}_3$ (1.30) manifested that the concentration of newly formed Ru-Ni interface defects is close to that of original Ni vacancy clusters. Hence, most Ru atoms may anchor onto vacancy clusters. The ratio of I_2/I_1 decreases with the increase in annealing temperature, indicating that the concentration of Ni vacancy clusters decreases. The I_2/I_1 ratios of $\text{Ni/H-Al}_2\text{O}_3$, $\text{Ni}_{\text{A500}}/\text{H-Al}_2\text{O}_3$, and $\text{Ni}_{\text{A550}}/\text{H-Al}_2\text{O}_3$ catalysts were positively correlated with the turnover frequency of C_1 (TOF_{C_1}) and CH_4 (TOF_{CH_4}), which suggested that vacancy clusters were the active sites for the cleavage of both C-C bond and C-O bonds in an ethanol steam reforming reaction. This work thus highlights the significance of quantifying concentration to probe catalytic



Fig. 8 (A) PAS spectra of ultrathin BiOCl nanosheets and nanoplates. (B and C) Schematic illustrations of trapped positrons of $V_{\text{Bi}}^{\bullet\bullet}$ defects and associated defects $V_{\text{Bi}}^{\bullet\bullet}V_{\text{O}}^{\bullet\bullet}V_{\text{Bi}}^{\bullet\bullet}$. (D) Positron lifetime parameters of ultrathin BiOCl nanosheets and nanoplates. (E) Calculated positron lifetime values of BiOCl.¹⁰⁴ Copyright © 2013 American Chemical Society.

reactions. PAS technology can only obtain the ratio of bulk-to-surface defects and the types of surface defects, which are limited in quantifying defect concentration. However, PAS plays an irreplaceable role in accurately locating defect types, which can be used as an auxiliary means to accurately quantify defect concentration in combination with other technologies such as XAFS and NMR.

2.5. Electron paramagnetic resonance (EPR)

EPR is a widely used technique that can qualitatively and quantitatively measure the unpaired electrons included in atoms or molecules and explore the structural features of their surroundings *via* the spin transitions of unpaired electrons.

Eichel's group studied the photoluminescence behaviour of ZnO films at different temperatures and calculated the defect density through EPR.¹⁰⁶ As shown in Fig. 9A, a single line is observed at $g = 1.9588$ in the corresponding EPR spectrum of the bulk ZnO powder (bottom), which indicates the presence of singly charged oxygen vacancy V_O . For nano-sized ZnO (top), accessional resonance lines appear at $g = 2.0028$, while the intensity of resonance lines at $g = 1.9588$ increases after UV irradiation of both nano-sized and bulk ZnO for 10 minutes (Fig. 9B), and the intensity of resonance lines at $g = 2.0028$ remains unchanged. Therefore, it is inferred that the resonance line at $g = 2.0028$ represents a defect on the ZnO surface. Similarly, Liu and colleagues synthesized a series of oxygen vacancy-rich Fenton-like catalysts CuFeO_2 by a cryogenic hydrothermal method, and used the EPR technology to compare the defect structure of these materials in depth.¹⁰⁷ As shown in Fig. 9C, all catalysts have a distinct EPR signal at $g = 2.003$, which indicates that oxygen vacancies are formed on the catalyst surface and that $\text{CuFeO}_2\text{@MRPs-200}$ contains the most abundant oxygen vacancies. The presence of oxygen vacancies not only promotes the charge transfer ability, but also promotes

the activation of H_2O_2 to $\cdot\text{OH}$, thus improving the ability of the material to catalyze rhodamine B degradation. Wang and co-workers also studied the Ti^{3+} species in anatase nanocrystals using EPR (Fig. 9D).¹⁰⁸ The " Ti^{3+} reversible diffusion mechanism" was used to control the location and concentration of Ti^{3+} defects by regulating temperature. The TiO_2 with the highest concentration of Ti^{3+} shows the best photocatalytic decomposition activity of methylene blue. This work emphasized that the reasonable distribution of Ti^{3+} subsurface/bulk defects is significant to high visible light-driven photocatalysis. In addition, the ESR can also be extended to recognize S vacancies. Peng's group used *in situ* EPR technology to reveal that the S vacancies of CdS-CNT samples increased with the CO_2RR , which strongly supported the continuous generation of S vacancies on the surface of CdS-CNT during the electrochemical reduction of CO_2 .¹⁰⁹

In general, the EPR can be a very intuitive means to observe unpaired electrons and defects, but the intensity of signal peak increases with the extension of scanning time, resulting in the deviation of using paramagnetic resonance to quantify the defect concentration, which is more useful as a qualitative tool. This limitation suggests that this technique should be used with other techniques for a comprehensive surface understanding.

2.6. X-ray photoelectron spectroscopy (XPS)

XPS can provide not only the elemental composition and valence information on the catalyst surface, but also the defect structure and chemical bond information of various compounds. The quantification of defects is also of great importance for a more in-depth study of defect effects in order to improve the performance of TiO_2 . Sung and co-workers by XPS analysis (Fig. 10A and B) reported that Cu doping increases the concentration of oxygen vacancies in TiO_2 nanorods.¹¹⁰ The concentration of oxygen vacancies of pristine and Cu doping TiO_2 nanorods was estimated based on the following formula:¹¹⁰

$$V_O (\%) = \{[(\text{the atomic number ratio of Ti} \times 4) - (\text{the atomic number ratio of O}_L \times 2)] / 2\} \times 100$$

Three forms of oxygen can be observed in the O 1s XPS spectra, namely, lattice oxygen (O_L , 530.3 eV), surface hydroxyl oxygen (O_{OH} , 532.1 eV) and adsorbed oxygen (O_S , 533.6 eV). The O_L corresponds to lattice oxygen, and it is considered to be an element sensitivity factor. After doping Cu, the concentration of oxygen vacancies increases from 31.2% for pristine TiO_2 nanorods to 37.66% for Cu-doped TiO_2 nanorods, which suggests that Cu doping facilitates the generation of oxygen vacancies in TiO_2 . In addition, Dai and co-workers also investigated the variation in oxygen vacancy concentration in ZnO prepared at different annealing temperatures.¹¹¹ According to the results of XPS fitting calculations, the concentration of oxygen vacancies decreases with the increase in annealing temperature, and the experimental results also indicate that ZnO materials with more oxygen vacancies have a longer absorption wavelength and a narrower band gap, resulting in the highest photodegradation activity for 2,4-dichlorophenol. Besides, Zeng and co-workers



Fig. 9 (A) EPR spectrum of different-sized ZnO. (B) Defect concentration (V_O) at $g = 1.9588$ before and after irradiation.¹⁰⁶ Copyright © 2009 Royal Society of Chemistry. (C) EPR spectra of CuFeO_2 , $\text{CuFeO}_2\text{@MRPs-100}$, $\text{CuFeO}_2\text{@MRPs-200}$ and $\text{CuFeO}_2\text{@MRPs-400}$.¹⁰⁷ Copyright © 2021 Elsevier Ltd. (D) EPR spectrum of P25, TiO_{2-x} and TiO_{2-x-7} .¹⁰⁸ Copyright © 2015 Elsevier B.V.



Fig. 10 (A) XPS of pure TiO_2 nanorods and (B) TiO_2 nanorods with Cu doping.¹¹⁰ Copyright © 2010 American Chemical Society. (C) XPS of V_O -rich ZnO.¹¹² Copyright © 2012 American Chemical Society. (D) XPS valence band spectra of black TiO_2 samples.¹¹³ Copyright © 2018 Elsevier Inc.

promoted the activation of CO_2 to produce CO by introducing oxygen vacancies on ZnO surfaces.¹¹² According to the XPS results shown in Fig. 10C, the integrated area ratios of 531.7 eV and 530.2 eV peaks are 0.30, 0.57 and 0.76, respectively, by fitting the ZnO nanosheets with three different oxygen defect contents (pristine, poor and rich). Moreover, XPS valence band spectroscopy can not only explore the surface defects of materials, but also reveal the electronic structure of materials. Ohno and coworkers investigated the concentrations of Ti^{3+} on the surface of TiO_2 and estimated the valence band maxima of the material to be about 1.6 eV based on linear extrapolation (Fig. 10D).¹¹³ The concentration of oxygen defects on the TiO_2 surface decreased with the increase in Ti^{3+} concentration, and the photocatalytic activity of TiO_2 reached the best when the concentration of Ti^{3+} was 22.6%. The quantitative analysis of the relative concentration of vacancy defects is thus critical to optimize the catalyst performance.

XPS is one of the most powerful tools for researching the surface properties of materials, allowing for detailed information about surface defects and electronic structures. However, its limitation is that the surface of many offline samples is easy to be oxidized and modified or adsorbed some small molecules. Therefore, the *in situ* technique can be developed to better understand the real surface information of the catalyst. Together with other representative techniques such as XAFS and PAS, one can better obtain a more comprehensive information of the defects.

2.7. Photoluminescence (PL) spectra

PL is widely used to characterize the bulk defect structure of metal oxide semiconductors. After absorbing the photon, the semiconductor material generates photoexcited electrons and holes in the conduction and valence bands, respectively. The excited electron-hole pairs will recombine at the defect center, resulting in trap-state luminescence.

Uyar and coworkers used the atomic layer deposition method with different deposition cycle numbers to prepare ZnO quantum dots (QDs) or nanocoating (NC) for the photo-degradation of methylene blue (MB).¹¹⁴ They found that Zn interstitials (Zn_i s) were dominant when the number of cycles was small, and oxygen vacancy (V_O) was gradually introduced as the cycle progresses. Analytical experiments for each defect were performed for each sample (Fig. 11A and B), and the relevant concentrations of Zn_i s and V_O were estimated by calculating the area of each peak, corresponding to the defect-related transitions. For illuminating the effect of Zn_i and V_O on photocatalytic activity, photoluminescence (PL) spectra were employed to quantify the density of defects.

The percentage increase in defect density was calculated by each peak's area of PL spectra based on the following formula:¹¹⁴

$$\% \text{increase for } b \text{ emission} = b' = \left(\frac{A_{b\text{fromPZ1QD}} - A_{b\text{fromPZ2,PZ3,PZ4NC}}}{A_{b\text{fromPZ1QD}}} \right) \times 100$$

Via analysis of the relation between photocatalytic activity (Fig. 11C) and the percentage increase in defect density (Fig. 11D), they concluded that V_O is more efficient than Zn_i -related defects for photocatalysis. In addition, importing oxygen vacancies into ZnO for the enhanced CO_2 reduction activity was reported by Zeng and coworkers.¹¹⁵ The recombination of two-electron-trapped oxygen vacancies and photogenerated holes in the PL spectra also confirms that ZnO with the rich oxygen vacancies has a higher PL intensity. The introduction of oxygen vacancies regulates the valence and conduction structures of ZnO, enhances the activation of CO_2 and promotes the electrocatalytic reduction of CO_2 to CO.

PL has been widely used to evaluate the defect structures due to its simple operation. However, the result could be interfered by bulk defects and vary with the excitation wavelength, indicating that PL testing alone is not enough to provide a comprehensive view on the structure-activity relationship. Therefore, it is strongly suggested to combine this technique with XPS, XAFS and other technologies for a better understanding of defect sites. Meanwhile, the recent development of *in situ* PL technique¹¹⁶ also makes it possible to measure the defective structure (or surface temperature) of materials under reactive conditions.

2.8. Fourier-transform infrared (FTIR) spectroscopy

The chemical bonds or functional groups in the material that absorbs infrared light at different frequencies will show specific positions, giving information about the vibrational properties of the adsorbed hydroxyl groups and metal-O (appearing at around $650\text{--}450\text{ cm}^{-1}$) of the catalyst. The bond force constant (k) determines the position and intensity of the IR absorption peak, indicating the change in the type and strength of the bond. Zhu and co-workers studied the variation in the V_O concentration on the ZnO surface by FTIR spectroscopy and found that the increase in V_O concentration leads to a decrease in Zn-O bond strength (k value), along with the position of IR



Fig. 11 (A) Luminescence spectra of ZnO with different numbers of cycles. (B) Schematic diagram of defect attribution. (C) Photocatalytic activities of different samples. (D) Defect density and corresponding decay constant. (E) Spectral locations of deconvoluted peaks and ascribed emission mechanism.¹¹⁴ Copyright © 2014 Royal Society of Chemistry.

absorption peak shifts to a lower wave number.¹¹⁷ Therefore, the defect concentration of the samples can be judged according to the infrared peak shift degree, providing a new view on the determination of the defect state. When other metallic elements such as Mn^{118,119} and Eu¹²⁰ entering the ZnO lattice, the IR absorption peak of the Zn–O bond in the fingerprint region will also change accordingly, which can be used to judge the successful doping of elements or not. It should be noted that the limitation of using FTIR spectroscopy to obtain defect information is that it is difficult to distinguish whether the change in fingerprint region is solely caused by defects when the catalyst composition and the surface state is complex. *In situ* FTIR techniques have been developed to monitor intermediates and active species in photo/electrocatalytic reaction processes,^{121,122} combined with other characterizations, and we can have a deeper understanding of the changes of catalyst and reactant molecules in the reaction process.

3. Summary and perspectives

In summary, defect engineering has become a key strategy to regulate the structure and properties of catalysts with the development of catalytic reactions in chemical production. This review focuses on a variety of representational methods to reveal the defects and summarizes from different perspectives on where, what and how much of the defects. Our method for calculating the defect concentration on the exposed facet based

on XAFS characterization also provides a new path for semi-quantifying the defect concentration of common catalytic materials. However, although considerable progress has been made in the study of defects, there are still some problems to be solved in terms of defect characterization technology and catalytic mechanism under working conditions.

(1) Due to the differences in the application scope of various characterization techniques, the characteristics of identifying defects are also different. Individual technology is limited by its own detection mechanism, making the obtained information unsatisfactory. For example, the V_o density and V_M density calculated based on the coordination number information obtained by XAFS are the average results of the whole individual phase, and the specific types of defects (like the surface of bulk state) cannot be well distinguished. ³¹P NMR can be used to obtain information such as defect types on specific facets of materials, but the results are more limited to the surface of materials. Therefore, to have a comprehensive understanding of the defect structure, we need to combine different representation techniques.

(2) The defect concentration obtained in the off-line state cannot truly reflect the defect state in the reaction process, and it is crucial to capture the defect information in the catalytic condition. Some *in situ* characterization techniques such as *in situ* XAFS, *in situ* ESR, *in situ* TEM, *in situ* NMR, and *in situ* XPS remain to be applied to reveal the dynamic evolution process of defects, so as to accurately understand and quantify defects.

However, *in situ* characterization is faced with many challenges. First of all, the equipment and instruments need to be upgraded, and it is urgent to develop *in situ* reaction devices suitable for liquid, light irradiation or gas environment, or high-temperature experiments. Second, the signal received in the *in situ* reaction process is much weaker than that in the off-line process, so it is necessary to design the concentration of catalyst active components reasonably to monitor the reaction process.

(3) The relationship between defects, reaction intermediates, and the reaction process has not been clarified. Given that transient processes such as charge transfer are also difficult to capture using *in situ* techniques, theoretical calculations (like DFT) will need to be developed next to better comprehend the catalytic processes. The development of transient time-resolved DFT calculation can also make up for the shortcomings of current characterization techniques and assist the understanding of defects in the catalytic process.

This review summarizes the current characterization of semi-quantified metals and metal oxide active sites under off-line conditions, and proposes a method to calculate the defect concentration using XAFS characterization and related methods, which provides some guidance for future defect engineering applications. The development of *in situ* technology and DFT will allow us to have a deeper understanding of defects and provide insights for the design of catalysts with high activity.

Author contributions

Jing Ren wrote and outlined the draft of the manuscript under the guidance of Yufei Zhao; Haoyuan Chi and Ling Tan contributed to investigate and data collation; Yung-Kang Peng, Guangchao Li and Molly Meng-Jung Li participated in data analysis and summary; Xue Duan developed the idea and supervised the project.

Conflicts of interest

The authors declare no conflict of interest.

Acknowledgements

This research was supported by the National Natural Science Foundation of China (22278030, 22090032, 22090030, 22288102, 22011530162), Major Program of Qingyuan Innovation Laboratory (Grant No. 001220005). We would like to thank the Space Exploration Program and the Qian Xuesen Laboratory, China Academy of the Space Technology.

References

- 1 J. C. Vedrine, *ChemSusChem*, 2019, **12**, 577–588.
- 2 J. N. Armor, *Appl. Catal.*, 1991, **78**, 141–173.
- 3 A. Chauvel, B. Delmon and W. F. Hölderich, *Appl. Catal., A*, 1994, **115**, 173–217.
- 4 M. Misono and N. Nojiri, *Appl. Catal.*, 1990, **64**, 1–30.
- 5 G. A. Somorjai, *Annu. Rev. Phys. Chem.*, 1994, **45**, 721–751.
- 6 G. Ertl, *Advances in Catalysis*, Academic Press, 2000, vol. 45, pp. 1–69.
- 7 C. Xiao, B.-A. Lu, P. Xue, N. Tian, Z.-Y. Zhou, X. Lin, W.-F. Lin and S.-G. Sun, *Joule*, 2020, **4**, 2562–2598.
- 8 Z.-Y. Zhou, N. Tian, J.-T. Li, I. Broadwell and S.-G. Sun, *Chem. Soc. Rev.*, 2011, **40**, 4167–4185.
- 9 Y. Sun, S. Gao, F. Lei and Y. Xie, *Chem. Soc. Rev.*, 2015, **44**, 623–636.
- 10 J. Ren, L. Tan, Y. Zhao and Y.-F. Song, *CIESC J.*, 2021, **72**, 398–424.
- 11 S. Bai, N. Zhang, C. Gao and Y. Xiong, *Nano Energy*, 2018, **53**, 296–336.
- 12 Z. Xiao, C. Xie, Y. Wang, R. Chen and S. Wang, *J. Energy Chem.*, 2021, **53**, 208–225.
- 13 K. Zhong, R. Bu, F. Jiao, G. Liu and C. Zhang, *Chem. Eng. J.*, 2022, **429**, 132310.
- 14 J. Huang, C. Fu, J. Chen, N. Senthilkumar, X. Peng and Z. Wen, *CCS Chem.*, 2022, **4**, 566–583.
- 15 J. Zhu and S. Mu, *Adv. Funct. Mater.*, 2020, **30**, 2001097.
- 16 Y.-C. Zhang, S. Ullah, R. Zhang, L. Pan, X. Zhang and J.-J. Zou, *Appl. Catal., B*, 2020, **277**, 119247.
- 17 B. Zhou, R. Gao, J.-J. Zou and H. Yang, *Small*, 2022, **18**, 2202336.
- 18 Y.-C. Zhang, N. Afzal, L. Pan, X. Zhang and J.-J. Zou, *Adv. Sci.*, 2019, **6**, 1900053.
- 19 Y. Liu, J.-g. Guo, Y. Wang, Y.-j. Hao, R.-h. Liu and F.-t. Li, *Green Energy Environ.*, 2021, **6**, 244–252.
- 20 J. W. Zuzeng Qin, B. Li, T. Su and H. Ji, *Acta Phys.-Chim. Sin.*, 2021, **37**, 2005027.
- 21 Y. Zhang, L. Guo, L. Tao, Y. Lu and S. Wang, *Small Methods*, 2019, **3**, 1800406.
- 22 P. Rao, D. Wu, T.-J. Wang, J. Li, P. Deng, Q. Chen, Y. Shen, Y. Chen and X. Tian, *eScience*, 2022, **2**, 399–404.
- 23 Y. Guo, M. Wang, Q. Zhu, D. Xiao and D. Ma, *Nat. Catal.*, 2022, **5**, 766–776.
- 24 C. Chen, L. Tao, S. Du, W. Chen, Y. Wang, Y. Zou and S. Wang, *Adv. Funct. Mater.*, 2020, **30**, 1909832.
- 25 H. Du, J. Fan, C. Miao, M. Gao, Y. Liu, D. Li and J. Feng, *Trans. Tianjin Univ.*, 2021, **27**, 24–41.
- 26 Y. Wang, Y. Zhang, Z. Liu, C. Xie, S. Feng, D. Liu, M. Shao and S. Wang, *Angew. Chem., Int. Ed.*, 2017, **56**, 5867–5871.
- 27 P. Zhou, Y. Wang, C. Xie, C. Chen, H. Liu, R. Chen, J. Huo and S. Wang, *Chem. Commun.*, 2017, **53**, 11778–11781.
- 28 R. Liu, Y. Wang, D. Liu, Y. Zou and S. Wang, *Adv. Mater.*, 2017, **29**, 1701546.
- 29 D. Zhou, X. Xiong, Z. Cai, N. Han, Y. Jia, Q. Xie, X. Duan, T. Xie, X. Zheng, X. Sun and X. Duan, *Small Methods*, 2018, **2**, 1800083.
- 30 X. Jia, X. Zhang, J. Zhao, Y. Zhao, Y. Zhao, G. I. N. Waterhouse, R. Shi, L.-Z. Wu, C.-H. Tung and T. Zhang, *J. Energy Chem.*, 2019, **34**, 57–63.
- 31 Q. Xie, Z. Cai, P. Li, D. Zhou, Y. Bi, X. Xiong, E. Hu, Y. Li, Y. Kuang and X. Sun, *Nano Res.*, 2018, **11**, 4524–4534.
- 32 Z. Ni, H. Liang, Z. Yi, R. Guo, C. Liu, Y. Liu, H. Sun and X. Liu, *Coord. Chem. Rev.*, 2021, **441**, 213983.

- 33 H. Zhang and M. M.-J. Li, *Curr. Opin. Green Sustainable Chem.*, 2022, **36**, 100646.
- 34 S. Chen, X. Liu, J. Xiong, L. Mi, X.-Z. Song and Y. Li, *J. Mater. Chem. A*, 2022, **10**, 6927–6949.
- 35 Q. Yang, T. Wang, Z. Zheng, B. Xing, C. Li and B. Li, *Appl. Catal., B*, 2022, **315**, 121575.
- 36 T. F. Jaramillo, K. P. Jørgensen, J. Bonde, J. H. Nielsen, S. Hørch and I. Chorkendorff, *Science*, 2007, **317**, 100–102.
- 37 R. Schaub, E. Wahlström, A. Rønnau, E. Lægsgaard, I. Stensgaard and F. Besenbacher, *Science*, 2003, **299**, 377–379.
- 38 E. Wahlstrom, E. K. Vestergaard, R. Schaub, A. Rønnau, M. Vestergaard, E. Laegsgaard, I. Stensgaard and F. Besenbacher, *Science*, 2004, **303**, 511–513.
- 39 F. F. Tao and M. Salmeron, *Science*, 2011, **331**, 171–174.
- 40 L. Tan, S. M. Xu, Z. Wang, Y. Xu, X. Wang, X. Hao, S. Bai, C. Ning, Y. Wang, W. Zhang, Y. K. Jo, S. J. Hwang, X. Cao, X. Zheng, H. Yan, Y. Zhao, H. Duan and Y. F. Song, *Angew. Chem., Int. Ed.*, 2019, **58**, 11860–11867.
- 41 M. Kong, Y. Li, X. Chen, T. Tian, P. Fang, F. Zheng and X. Zhao, *J. Am. Chem. Soc.*, 2011, **133**, 16414–16417.
- 42 X. Liu and L. Gu, *Small Methods*, 2018, **2**, 1800006.
- 43 Q. Sun, Z. Gong, Y. Zhang, J. Hao, S. Zheng, W. Lu, Y. Cui, L. Liu and Y. Wang, *J. Hazard. Mater.*, 2022, **421**, 126816.
- 44 J. Xie, X. Zhang, H. Zhang, J. Zhang, S. Li, R. Wang, B. Pan and Y. Xie, *Adv. Mater.*, 2017, **29**, 1604765.
- 45 S. Chen, H. Wang, Z. Kang, S. Jin, X. Zhang, X. Zheng, Z. Qi, J. Zhu, B. Pan and Y. Xie, *Nat. Commun.*, 2019, **10**, 788.
- 46 H. Feng, Z. Xu, L. Ren, C. Liu, J. Zhuang, Z. Hu, X. Xu, J. Chen, J. Wang, W. Hao, Y. Du and S. X. Dou, *ACS Catal.*, 2018, **8**, 4288–4293.
- 47 R. Schaub, P. Thosttrup, N. Lopez, E. Lægsgaard, I. Stensgaard, J. K. Nørskov and F. Besenbacher, *Phys. Rev. Lett.*, 2001, **87**, 266104.
- 48 X. Li, A. Gao, Z. Tang, F. Meng, T. Shang, S. Guo, J. Ding, Y. Luo, D. Xiao, X. Wang, D. Su, Q. Zhang and L. Gu, *Adv. Funct. Mater.*, 2021, **31**, 2010291.
- 49 J. Lee, Y. Gong, L. Gu and B. Kang, *ACS Energy Lett.*, 2021, **6**, 789–798.
- 50 H. Frey, A. Beck, X. Huang, J. A. van Bokhoven and M. G. Willinger, *Science*, 2022, **376**, 982–987.
- 51 A. Beck, X. Huang, L. Artiglia, M. Zabilskiy, X. Wang, P. Rzepka, D. Palagin, M. G. Willinger and J. A. van Bokhoven, *Nat. Commun.*, 2020, **11**, 3220.
- 52 X. Huang, T. Jones, A. Fedorov, R. Farra, C. Coperet, R. Schlogl and M. G. Willinger, *Adv. Mater.*, 2021, **33**, e2101772.
- 53 H. Fan, L. Qiu, A. Fedorov, M. G. Willinger, F. Ding and X. Huang, *ACS Nano*, 2021, **15**, 17895–17906.
- 54 J. Wang, Y. Xu, J. Li, X. Ma, S.-M. Xu, R. Gao, Y. Zhao and Y.-F. Song, *Green Chem.*, 2020, **22**, 8604–8613.
- 55 L. Tan, S.-M. Xu, Z. Wang, Y. Xu, X. Wang, X. Hao, S. Bai, C. Ning, Y. Wang, W. Zhang, Y. K. Jo, S.-J. Hwang, X. Cao, X. Zheng, H. Yan, Y. Zhao, H. Duan and Y.-F. Song, *Angew. Chem., Int. Ed.*, 2019, **58**, 11860–11867.
- 56 Q. Wang and D. O'Hare, *Chem. Rev.*, 2012, **112**, 4124–4155.
- 57 X. Hao, L. Tan, Y. Xu, Z. Wang, X. Wang, S. Bai, C. Ning, J. Zhao, Y. Zhao and Y.-F. Song, *Ind. Eng. Chem. Res.*, 2020, **59**, 3008–3015.
- 58 R. Liu, Y. Wang, D. Liu, Y. Zou and S. Wang, *Adv. Mater.*, 2017, **29**, 1701546.
- 59 Y. Wang, Y. Zhang, Z. Liu, C. Xie, S. Feng, D. Liu, M. Shao and S. Wang, *Angew. Chem., Int. Ed.*, 2017, **56**, 5867–5871.
- 60 Y. Zhao, Y. Zhao, G. I. N. Waterhouse, L. Zheng, X. Cao, F. Teng, L.-Z. Wu, C.-H. Tung, D. O'Hare and T. Zhang, *Adv. Mater.*, 2017, **29**, 1703828.
- 61 Y. Zhao, X. Zhang, X. Jia, G. I. N. Waterhouse, R. Shi, X. Zhang, F. Zhan, Y. Tao, L.-Z. Wu, C.-H. Tung, D. O'Hare and T. Zhang, *Adv. Energy Mater.*, 2018, **8**, 1703585.
- 62 X. Zhang, Y. Zhao, Y. Zhao, R. Shi, G. I. N. Waterhouse and T. Zhang, *Adv. Energy Mater.*, 2019, **9**, 1900881.
- 63 T. Rossi, T. J. Penfold, M. H. Rittmann-Frank, M. Reinhard, J. Rittmann, C. N. Borca, D. Grolimund, C. J. Milne and M. Chergui, *J. Phys. Chem. C*, 2014, **118**, 19422–19430.
- 64 G. Giuli, A. Trapananti, F. Mueller, D. Bresser, F. d'Acapito and S. Passerini, *Inorg. Chem.*, 2015, **54**, 9393–9400.
- 65 A. K. Rana, Y. Kumar, P. Rajput, S. N. Jha, D. Bhattacharyya and P. M. Shirage, *ACS Appl. Mater. Interfaces*, 2017, **9**, 7691–7700.
- 66 M. A. Peck and M. A. Langell, *Chem. Mater.*, 2012, **24**, 4483–4490.
- 67 A. Gutiérrez, G. Domínguez-Cañizares, J. A. Jiménez, I. Preda, D. Díaz-Fernández, F. Jiménez-Villacorta, G. R. Castro, J. Chaboy and L. Soriano, *Appl. Surf. Sci.*, 2013, **276**, 832–837.
- 68 Y. Zhao, X. Jia, G. Chen, L. Shang, G. I. N. Waterhouse, L.-Z. Wu, C.-H. Tung, D. O'Hare and T. Zhang, *J. Am. Chem. Soc.*, 2016, **138**, 6517–6524.
- 69 Z. Wang, S.-M. Xu, L. Tan, G. Liu, T. Shen, C. Yu, H. Wang, Y. Tao, X. Cao, Y. Zhao and Y.-F. Song, *Appl. Catal., B*, 2020, **270**, 118884.
- 70 A. K. Rana, Y. Kumar, P. Rajput, S. N. Jha, D. Bhattacharyya and P. M. Shirage, *ACS Appl. Mater. Interfaces*, 2017, **9**, 7691–7700.
- 71 B. L. Caetano, C. V. Santilli, F. Meneau, V. Briois and S. H. Pulcinelli, *J. Phys. Chem. C*, 2011, **115**, 4404–4412.
- 72 M. Kuwa, M. Harada, R. Sato and T. Teranishi, *ACS Appl. Nano Mater.*, 2020, **3**, 2745–2755.
- 73 D. Delgado, R. Sanchis, J. A. Cecilia, E. Rodríguez-Castellón, A. Caballero, B. Solsona and J. M. L. Nieto, *Catal. Today*, 2019, **333**, 10–16.
- 74 G. Wu, W. Chen, X. Zheng, D. He, Y. Luo, X. Wang, J. Yang, Y. Wu, W. Yan, Z. Zhuang, X. Hong and Y. Li, *Nano Energy*, 2017, **38**, 167–174.
- 75 A. Gutiérrez, G. Domínguez-Cañizares, J. A. Jiménez, I. Preda, D. Díaz-Fernández, F. Jiménez-Villacorta, G. R. Castro, J. Chaboy and L. Soriano, *Appl. Surf. Sci.*, 2013, **276**, 832–837.
- 76 M. A. Peck and M. A. Langell, *Chem. Mater.*, 2012, **24**, 4483–4490.
- 77 T. Ding, X. Liu, Z. Tao, T. Liu, T. Chen, W. Zhang, X. Shen, D. Liu, S. Wang, B. Pang, D. Wu, L. Cao, L. Wang, T. Liu,

- Y. Li, H. Sheng, M. Zhu and T. Yao, *J. Am. Chem. Soc.*, 2021, **143**, 11317–11324.
- 78 S. Fang, X. Zhu, X. Liu, J. Gu, W. Liu, D. Wang, W. Zhang, Y. Lin, J. Lu, S. Wei, Y. Li and T. Yao, *Nat. Commun.*, 2020, **11**, 1029.
- 79 B. L. Caetano, C. V. Santilli, F. Meneau, V. Briois and S. H. Pulcinelli, *J. Phys. Chem. C*, 2011, **115**, 4404–4412.
- 80 P. J. Sideris, U. G. Nielsen, Z. Gan and C. P. Grey, *Science*, 2008, **321**, 113–117.
- 81 S. Cadars, G. Layrac, C. Gérardin, M. Deschamps, J. R. Yates, D. Tichit and D. Massiot, *Chem. Mater.*, 2011, **23**, 2821–2831.
- 82 G. Yu, F. Hu, H. Huo, W. Ding and L. Peng, *Chem. Phys. Lett.*, 2018, **706**, 47–52.
- 83 L. Jin, Y. Sun, X. Zhou, J. Wen, F. Wang, X. Ning, Y. Wen, D. Wu and L. Peng, *ACS Sustainable Chem. Eng.*, 2022, **10**, 12955–12961.
- 84 Y.-K. Peng and S. C. E. Tsang, *Nano Today*, 2018, **18**, 15–34.
- 85 X. Yi, H.-H. Ko, F. Deng, S.-B. Liu and A. Zheng, *Nat. Protoc.*, 2020, **15**, 3527–3555.
- 86 A. Zheng, S.-B. Liu and F. Deng, *Chem. Rev.*, 2017, **117**, 12475–12531.
- 87 A. Zheng, S.-J. Huang, S.-B. Liu and F. Deng, *Phys. Chem. Chem. Phys.*, 2011, **13**, 14889–14901.
- 88 Y. K. Peng, L. Ye, J. Qu, L. Zhang, Y. Fu, I. F. Teixeira, I. J. McPherson, H. He and S. C. Tsang, *J. Am. Chem. Soc.*, 2016, **138**, 2225–2234.
- 89 Y.-K. Peng, Y. Fu, L. Zhang, I. F. Teixeira, L. Ye, H. He and S. C. E. Tsang, *ChemCatChem*, 2017, **9**, 155–160.
- 90 Y. K. Peng, Y. Hu, H. L. Chou, Y. Fu, I. F. Teixeira, L. Zhang, H. He and S. C. E. Tsang, *Nat. Commun.*, 2017, **8**, 675.
- 91 Y. K. Peng, H. L. Chou and S. C. Edman Tsang, *Chem. Sci.*, 2018, **9**, 2493–2500.
- 92 Z. Tan, J. Zhang, Y.-C. Chen, J.-P. Chou and Y.-K. Peng, *J. Phys. Chem. Lett.*, 2020, **11**, 5390–5396.
- 93 Z. Tan, T.-S. Wu, Y.-L. Soo and Y.-K. Peng, *Appl. Catal., B*, 2020, **264**, 118508.
- 94 Z. Tan, G. Li, H.-L. Chou, Y. Li, X. Yi, A. H. Mahadi, A. Zheng, S. C. Edman Tsang and Y.-K. Peng, *ACS Catal.*, 2020, **10**, 4003–4011.
- 95 Q. Wang, X. Yi, Y.-C. Chen, Y. Xiao, A. Zheng, J. L. Chen and Y.-K. Peng, *Angew. Chem., Int. Ed.*, 2021, **60**, 16149–16155.
- 96 Y.-K. Peng, B. Keeling, Y. Li, J. Zheng, T. Chen, H.-L. Chou, T. J. Puchtler, R. A. Taylor and S. C. E. Tsang, *Chem. Commun.*, 2019, **55**, 4415–4418.
- 97 Y. Li, Y.-K. Peng, L. Hu, J. Zheng, D. Prabhakaran, S. Wu, T. J. Puchtler, M. Li, K.-Y. Wong, R. A. Taylor and S. C. E. Tsang, *Nat. Commun.*, 2019, **10**, 4421.
- 98 X. Yi, K. Liu, W. Chen, J. Li, S. Xu, C. Li, Y. Xiao, H. Liu, X. Guo, S.-B. Liu and A. Zheng, *J. Am. Chem. Soc.*, 2018, **140**, 10764–10774.
- 99 Y.-K. Peng and S.-c. E. Tsang, *Magn. Reson. Lett.*, 2022, **2**, 9–16.
- 100 X. Chen, Y.-y. Fu, B. Yue and H. He, *Chin. J. Magn. Reson.*, 2021, **38**, 491–502.
- 101 H. T. Kreissl, M. M. J. Li, Y.-K. Peng, K. Nakagawa, T. J. N. Hooper, J. V. Hanna, A. Shepherd, T.-S. Wu, Y.-L. Soo and S. C. E. Tsang, *J. Am. Chem. Soc.*, 2017, **139**, 12670–12680.
- 102 G. Li, C. Foo, X. Yi, W. Chen, P. Zhao, P. Gao, T. Yoskamtorn, Y. Xiao, S. Day, C. C. Tang, G. Hou, A. Zheng and S. C. E. Tsang, *J. Am. Chem. Soc.*, 2021, **143**, 8761–8771.
- 103 G. Li, T. Yoskamtorn, W. Chen, C. Foo, J. Zheng, C. Tang, S. Day, A. Zheng, M. M.-J. Li and S. C. E. Tsang, *Angew. Chem., Int. Ed.*, 2022, **61**, e202204500.
- 104 M. Guan, C. Xiao, J. Zhang, S. Fan, R. An, Q. Cheng, J. Xie, M. Zhou, B. Ye and Y. Xie, *J. Am. Chem. Soc.*, 2013, **135**, 10411–10417.
- 105 H. Chen, S. He, X. Cao, S. Zhang, M. Xu, M. Pu, D. Su, M. Wei, D. G. Evans and X. Duan, *Chem. Mater.*, 2016, **28**, 4751–4761.
- 106 J. J. Schneider, R. C. Hoffmann, J. Engstler, S. Dilfer, A. Klyszcz, E. Erdem, P. Jakes and R. A. Eichel, *J. Mater. Chem.*, 2009, **19**, 1449–1457.
- 107 M. Wang, C. Liu, H. Shi, T. Long, C. Zhang and B. Liu, *Chemosphere*, 2021, **283**, 131191.
- 108 X. Xin, T. Xu, J. Yin, L. Wang and C. Wang, *Appl. Catal., B*, 2015, **176–177**, 354–362.
- 109 B. Qin, Y. Li, H. Wang, G. Yang, Y. Cao, H. Yu, Q. Zhang, H. Liang and F. Peng, *Nano Energy*, 2019, **60**, 43–51.
- 110 M. You, T. G. Kim and Y.-M. Sung, *Cryst. Growth Des.*, 2010, **10**, 983–987.
- 111 J. Wang, Z. Wang, B. Huang, Y. Ma, Y. Liu, X. Qin, X. Zhang and Y. Dai, *ACS Appl. Mater. Interfaces*, 2012, **4**, 4024–4030.
- 112 Z. G. Geng, X. D. Kong, W. W. Chen, H. Y. Su, Y. Liu, F. Cai, G. X. Wang and J. Zeng, *Angew. Chem., Int. Ed.*, 2018, **57**, 6054–6059.
- 113 S. Liu, S. Yuan, Q. Zhang, B. Xu, C. Wang, M. Zhang and T. Ohno, *J. Catal.*, 2018, **366**, 282–288.
- 114 F. Kayaci, S. Vempati, I. Donmez, N. Biyikli and T. Uyar, *Nanoscale*, 2014, **6**, 10224–10234.
- 115 Z. G. Geng, X. D. Kong, W. W. Chen, H. Y. Su, Y. Liu, F. Cai, G. X. Wang and J. Zeng, *Angew. Chem., Int. Ed.*, 2018, **57**, 6054–6059.
- 116 B. Terlingen, T. Arens, T. P. van Swieten, F. T. Rabouw, T. Prins, M. M. de Beer, A. Meijerink, M. Ahr, E. M. Hutter, C. van Lare and B. M. Weckhuysen, *Angew. Chem., Int. Ed.*, 2022, **61**, e202211991.
- 117 Y. Zheng, C. Chen, Y. Zhan, X. Lin, Q. Zheng, K. Wei, J. Zhu and Y. Zhu, *Inorg. Chem.*, 2007, **46**, 6675–6682.
- 118 S. Yildirimcan, K. Ocakoglu, S. Erat, F. M. Emen, S. Repp and E. Erdem, *RSC Adv.*, 2016, **6**, 39511–39521.
- 119 N. D. Raskar, D. V. Dake, V. A. Mane, E. Stathatos, U. Deshpande and B. Dole, *J. Mater. Sci.: Mater. Electron.*, 2019, **30**, 10886–10899.
- 120 O. Sacco, P. Franco, I. De Marco, V. Vaiano, E. Callone, R. Ceccato and F. Parrino, *J. Mater. Sci. Technol.*, 2022, **112**, 49–58.
- 121 L. Tan, S.-M. Xu, Z. Wang, X. Hao, T. Li, H. Yan, W. Zhang, Y. Zhao and Y.-F. Song, *Cell Rep. Phys. Sci.*, 2021, **2**, 100322.
- 122 T. Li, L. Tan, Y. Zhao and Y.-F. Song, *Chem. Eng. Sci.*, 2021, **245**, 116839.