

PAPER

View Article Online
View Journal | View Issue



Cite this: *Energy Environ. Sci.*,
2024, 17, 7221

Film-forming polymer nanoparticle strategy for improving the passivation and stability of perovskite solar cells†

Zhenyu Jia, ^{id}*^a Ran Wang, ^{id}^a Lei Zhu, ^{id}^b Amal Altujjar, ^{id}^{ac} Polina Jacoutot, ^d Osama M. Alkhudhari, ^{id}^{ae} Muhamad Z. Mokhtar, ^{af} Ben F. Spencer, ^{id}^{ag} Nigel W. Hodson, ^h Xuelian Wang, ^a Mollie Osborne-Richards, ^a Andrew G. Thomas, ^{ag} Teruo Hashimoto, ^a Michael Faulkner, ^a David J. Lewis, ^{id}^a Saif A. Haque, ^{id}^d M. Saiful Islam, ^{id}^b Jennifer M. Saunders^a and Brian R. Saunders ^{id}*^a

Perovskite solar cells (PSCs) provide excellent potential for large-scale solar energy harvesting because of their high power conversion efficiency (PCE) and facile preparation. However, long-term stability remains the Achilles heel for PSCs and new methods for improving stability are urgently needed. Film-forming polymer nanoparticles are widely used in the surface coatings industry to provide scalable, low-cost protection to surfaces. Inspired by this, here we add three soft, film-forming crosslinked polymer nanoparticle systems (nanogels) with different diameters (60, 100 and 200 nm) to the perovskite (FA_{0.75}MA_{0.25}PbI₃) precursor solution and study their effects on PSC performance. The nanogels contain hydrophilic ethylene oxide repeat units and form films when their diameter is less than or equal to 100 nm. Device stability was assessed using shelf-life and light-soaking measurements; in addition, films were subjected to moisture challenge tests. We show that nanogel coverage increases the PCE and stability. *Ab initio* simulations indicate strong binding of the molecules that comprise the nanogels on the perovskite surface through Pb–O bonds, thereby promoting enhanced surface stability in agreement with the XPS and FTIR signals associated with the binding of the C=O and C–O groups to Pb. Shelf-life stability measurements showed that nanogels with a diameter of 100 nm gave devices that retained >80% of their initial PCE after more than six months compared to 25% for the control. In contrast, the 200 nm nanogels did not form films or increase the PCE or shelf-life stability. The 100 nm nanogels also gave the best stability to light soaking. Our results show that highly deformable hydrophilic film-forming nanogel particles with a size of ~100 nm provide a scalable alternative approach for improving passivation and stability of PSCs.

Received 7th March 2024,
Accepted 26th July 2024

DOI: 10.1039/d4ee01073f

rsc.li/ees

Broader context

Whilst silicon solar cells continue to dominate deployment of solar cell technology, the rise of perovskite solar cells (PSCs) is beginning to gain commercial momentum. Nevertheless, stability improvements for PSCs are required in order to successfully compete with the 25-year warranties offered for silicon solar cells. A major source of instability for PSCs is surface defects and new approaches for decreasing trap density *via* passivation are urgently needed. Nanogels (swellable crosslinked polymer nanoparticles) that are highly deformable and expose previously hidden binding groups upon deposition are a new macro-passivating additive for PSCs. Here, we investigate the effect of nanogel size on the passivation and stability of PSCs and report that the optimum size is 100 nm. We demonstrate that our film-forming nanogels decrease trap density and increase PSC stability. Using a combination of *ab initio* simulation and experimental techniques, we discuss the mechanisms and relations that underpin these findings.

^a Department of Materials, University of Manchester, Engineering Building A, Manchester M1 7HL, UK. E-mail: zhenyu.jia@postgrad.manchester.ac.uk, brian.saunders@manchester.ac.uk

^b Department of Materials, University of Oxford, Oxford OX1 3PH, UK

^c Basic Science Department, Deanship of Preparatory Year and Supporting Studies, Imam Abdulrahman Bin Faisal University, Dammam 34221, Kingdom of Saudi Arabia

^d Department of Chemistry, Imperial College London, Molecular Sciences Research Hub, Wood Lane W12 0BZ, UK

^e Department of Chemistry, Taif University, Taif 21974, Saudi Arabia

^f Department of Water and Environmental Engineering, M46, Faculty of Civil Engineering, Universiti Teknologi Malaysia, 81310 Johor Bahru, Malaysia

^g Photon Science Institute, The Henry Royce Institute, University of Manchester, Manchester M13 9PL, UK

^h BioAFM Facility, Faculty of Biology, Medicine and Health, University of Manchester, Stopford Building, Oxford Road, Manchester M13 9PT, UK

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4ee01073f>



Introduction

Perovskite solar cells (PSCs) have received tremendous attention owing to their outstanding properties such as high absorption coefficient, large carrier diffusion length, tuneable bandgap, as well as facile and potentially low cost construction.^{1–9} Since the seminal study of Miyasaka *et al.* in 2009,¹⁰ the power conversion efficiency (PCE) for PSCs has increased dramatically from 3.8% to 26.1%.¹¹ Accordingly, PSCs have considerable potential for commercial exploitation. However, one of the main obstacles to such exploitation is their relatively poor stability,¹² which originates from mobile ions,^{13,14} defects,^{15–17} sensitivity to oxygen,¹⁸ water^{19,20} and light^{21,22} as well as poor mechanical toughness.²³ Enhanced ion migration and non-radiative recombination can occur at defect sites, leading to degradation and PCE reduction.^{24,25} Defects at interfaces and grain boundaries can become conduits where moisture invades.^{26,27} To address these issues, additives have been used to engineer the perovskite layer which has resulted in increases in PCE and stability.^{1,28–31} However, even the highest PCE systems still degrade over relatively short periods of time compared to silicon solar cells which have warranties of 25 years.³² Our motivation for the present study is to address the urgent need to explore new types of additives for improving PSC stability.

Self-assembled monolayers (SAMs) have shown promise as an effective approach to improve PSC stability.³³ An iodine-terminated SAM was used to increase the adhesion toughness at the interface between the electron transfer layer (ETL) and perovskite as well as stability.³⁴ The approach has been extended to include flexible PSCs.³⁵ In addition, a ruthenium dye-based SAM has been used as an interlayer between perovskite and the hole transfer layer (HTL) to increase PSC stability.³⁶

Additive engineering aims to use species added to the perovskite precursor solution or interfaces to decrease the defect density and thereby increase PCE and stability.^{17,37} Additives have principally involved small molecules^{1,28,38,39} and conventional polymers.^{40,41} Small molecules that have been successful in improving the properties include phenethylammonium iodide,⁴² methylammonium chloride¹ and diammonium spacer ligands.³⁷ Examples of polymers used include polyacrylic acid,^{40,43,44} polyethyleneimine,^{40,43} polyethylene glycol,^{40,45,46} polyacrylonitrile⁴⁷ and poly(ethylene dimethacrylate-polyhedral oligomeric silsesquioxane).⁴⁸

Polymer additives can increase the nucleation rate and retard crystal growth^{49,50} to enlarge crystal grain size and effectively reduce the defect density at the grain boundaries. In addition, polymers can also improve the adhesion strengths and reinforce the interfaces of PSCs.⁵¹ However, the use of polymers as additives in PSCs poses a dilemma. The strong multiple interactions that would benefit the mechanical and device stability of the perovskite films also prevent formation of compact perovskite films due to interference with perovskite crystallization.⁴⁰ This problem could be overcome by using deformable polymer nanoparticles such as nanogels that flatten and form films after perovskite crystallization to present previously hidden functional groups to the perovskite surface; such an approach is the focus of the present study. Nanogels are nanosized crosslinked polymer colloid particles that swell

in a good solvent.⁵² Comparing dispersions of polymer nanogels to polymer solutions, the former have much lower viscosities which enables facile delivery of the polymer to surfaces.

We have used poly(*N*-isopropylacrylamide) (PNP) microgels to improve the performance of semi-transparent PSCs.^{53,54} (Microgels are nanogels at a larger length scale.) Here, a new alternative family of nanogels is investigated (Fig. 1a) in non-semi-transparent PSCs that deliver much higher PCEs. The nanogels used in the present study are comprised of a different polymer to PNP and uniquely display film-forming behavior in the perovskite layer. The advantage of using nanogels or microgels is that, provided the particles swell in the precursor solvent (which acts as a good solvent), they do not agglomerate during perovskite film formation because of strong steric stabilization. The latter originates from the entropy decrease from a loss of configurational freedom if polymer chains of (swollen) neighboring nanogels interpenetrate. We have also found that the size of these particles determines the morphology of the perovskite films with large microgels dictating the morphology⁵³ whilst smaller nanogels can be dispersed throughout the film.⁵⁵ The present study exploits the excellent colloidal stability of film-forming nanogels to passivate the perovskite and improve stability.

Here, we employ poly(2-(2-methoxyethoxy)ethylmethacrylate) (PMEO₂MA) nanogels (Fig. 1a) as film-forming nanoparticles. (Note that $x \gg y$ for the structure in Fig. 1a.) PMEO₂MA has a low glass transition temperature⁵⁶ and a strong tendency to deform when deposited.⁵⁷ By flattening on surfaces nanogels increase their surface area and expose previously buried functional groups. Furthermore, nanogels can partially coalesce on surfaces when the solvent evaporates.⁵⁸ Such a process has been the basis for surface coatings for decades^{59,60} and is investigated here in PSCs for the first time. The nanogel additive approach used in this study is inherently simple because the nanogels are added to the perovskite precursor solution prior to deposition. Our approach has similarities to the use of polymer binders in the preparation of organic field-effect transistors,^{61–63} in which linear polymers are employed to provide property tuning. The approach used in this study is distinct in that we use polymer colloid nanogel particles and apply them to the challenge of PSC stability improvement.

We apply a facile nanogel film-forming strategy for delivering PMEO₂MA to perovskite grain surfaces. Three nanogel systems with different diameters are used (Fig. 1a). We report that the film-forming nanogels provide much improved performance compared to the non-film-forming system. We explain these results in terms of increased contact and passivation of the PMEO₂MA chains with the perovskite. FTIR and *ab initio* simulation results show that PMEO₂MA binds to Pb²⁺ and transient absorption spectroscopy studies reveal that the thin nanogel film does not obstruct hole transport. The film-forming nanogels are also shown to improve the mechanical properties of the perovskite films as assessed by adhesion tests. The deformable film-forming nanogel approach introduced in this study is scalable and should be applicable to other PSCs.



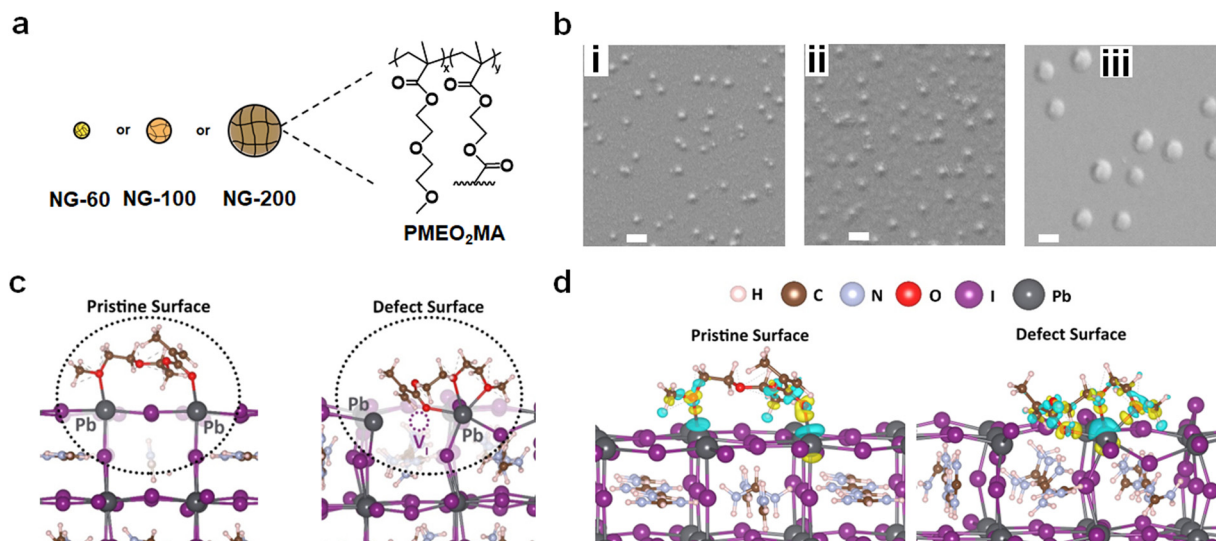


Fig. 1 (a) Three dispersions with different PMEO₂MA nanogel diameters are used in this study: small (NG-60), relatively large (NG-100) and very large (NG-200). (b) SEM images for (i) NG-60, (ii) NG-100 and (iii) NG-200 particles. Scale bars 200 nm. (c) Depiction of the nature of MEO₂MA bonding on the pristine (left) and the defect (right) (001) PbI₂-terminated FAPbI₃ surface. (d) Side view of the lowest-energy configuration and charge transfer density difference of MEO₂MA bonding on the pristine (left) and the defect (right) surface. Charge density gain and loss are colored in yellow and blue, respectively.

Results and discussion

Nanogel characterization and insights into interactions between PMEO₂MA and the perovskite surface

Three PMEO₂MA nanogel systems were prepared (see Experimental details and Table S1, ESI[†]) and are denoted as NG-60, NG-100 and NG-200 based on their diameters in nm (Fig. 1a). Scanning electron microscopy (SEM) images obtained by drying diluted nanogel dispersions gave average diameters of 60, 103 and 202 nm, respectively, for NG-60, NG-100 and NG-200 (Fig. 1b and Table S2, ESI[†]), with their size distributions shown in Fig. S1 (ESI[†]). Atomic force microscopy (AFM) data measured for the NG-200 particles deposited from water are shown in Fig. S2 (ESI[†]). The average particle diameter and height are 237 and 69 nm, respectively, giving an aspect ratio (diameter/height) of 3.4. Hence, the PMEO₂MA nanogel particles tend to flatten when deposited from the swollen state⁶⁴ as can be seen from the line profile of a NG-200 particle (Fig. S2, ESI[†]). Additional discussion and characterization data for the nanogels are given in the ESI[†] (Note 1 and Fig. S3, ESI[†]).

To gain preliminary atomic-scale insights into the interactions of these nanogels at the perovskite surface, density functional theory (DFT) simulation techniques were employed. An optimized monomeric representation of the PMEO₂MA molecule, namely, MEO₂MA (Fig. S4, ESI[†]), was placed on top of formamidinium lead tri-iodide (FAPbI₃), which constitutes about 75% of the perovskite composition in our experiments. It is known that iodine vacancy defects play a role in non-radiative recombination and ion migration, which can decrease the PSC device efficiency.^{65,66} Therefore, our computational investigation focuses on the interactions with the pristine surface as well as the surface where an iodine vacancy defect is present. The (001) PbI₂-terminated surface was constructed, as this surface configuration

has been reported to be one of the most thermodynamically stable and highly studied halide perovskite surfaces.⁶⁷ (Computational details are provided in the Experimental details in the ESI[†].)

Fig. 1c (left) illustrates the optimized configuration of MEO₂MA on the perovskite surface, which shows the molecule reshaped into a less planar configuration with two O atoms interacting with two nearest Pb²⁺ ions at the perovskite surface. An increased band gap of about 30 meV was found compared to that for the pure FAPbI₃ surface, suggesting that a blue shift may be found spectroscopically, which is shown to be in agreement with our measurements below.

The binding energy at the perovskite surface is found to be −1.42 eV, indicating favourable bonding affinity between the MEO₂MA molecule and surface. The Pb–O distances between the O atom of the methacrylate moiety carbonyl (C=O) group and the O atom of the 2-(2-methoxyethoxy)ethanol moiety C–O group with their bonded Pb²⁺ ions are 2.55 Å and 2.70 Å respectively. Notably, both of these values are significantly shorter than the Pb–I bond length (3.14 Å) in bulk FAPbI₃, indicating the stabilization of the undercoordinated surface Pb²⁺ ions. The chemical bonding was further confirmed by the high charge density around the oxygen atoms and the charge transfer profile at both Pb–O bonds from the charge density difference (Fig. 1d, left). Such O–Pb bonding is shown to be in agreement with our XPS and FTIR data below.

To further investigate the interactions, *ab initio* molecular dynamics (AIMD) simulations were carried out at 300 K, starting at the lowest-energy monomer-surface configuration. On the pristine and defective surfaces, the dynamics of the molecule and surface relaxations (shown in ESI[†] Videos S1 and S2) indicate that the additive molecule remains close to the perovskite surface, regardless of the presence of the facile vacancy defect.

The interactions on the defective surface indicate the two O atoms from the 2-(2-methoxyethoxy)ethanol moiety (C–O) form



bonds with the same nearest Pb^{2+} ions, while the O atom of the carbonyl group ($\text{C}=\text{O}$) stabilizes near the iodide vacancy site, effectively reducing the surface vacancy density. This oxygen is likely to bond with either of the nearest Pb^{2+} ions adjacent to the vacancy site, but the lowest-energy configuration was found in which three oxygen atoms bond to the Pb^{2+} ions (Fig. 1c, right). The binding energy is -2.23 eV, which is about 0.8 eV more favourable than that for the pristine surface indicating strong defect passivation. It should be noted that the bonding scenario where one O atom bonds to the other adjacent Pb^{2+} ion was found slightly less favourable (-1.97 eV) and shown in Fig. S5 (ESI[†]). The bonding between O atoms and the Pb^{2+} ion is further confirmed by the O–Pb bond lengths (2.65 – 2.92 Å) and the charge density transfer at the O–Pb bonds from the DFT simulations (Fig. 1d, right). Such strong molecule–perovskite interactions increase the anchoring strength on the surface, stabilize the undercoordinated Pb, and passivate the surface iodine vacancy, all of which are expected to improve the perovskite performance and stability.

We next investigate experimental data for nanogel film formation, perovskite films and devices prepared using precursor solutions containing the nanogels. The precursor compositions used for all of the perovskite films are given in Table S3 (ESI[†]).

Nanogel film formation

The nanogel concentrations employed in this work are given in terms of the mass concentration of nanogel in the precursor solution (mg g^{-1}). A preliminary study using the NG-100 system established that a nanogel concentration of 3.0 mg g^{-1} was optimum for device PCE (see Note 2 and Fig. S6 and S7, as well as Table S4, ESI[†]). (The effect of nanogel concentration for the NG-60 and NG-200 systems is studied later.) A nanogel concentration of 3.0 mg g^{-1} is used unless otherwise stated.

We investigated the effect of spin-coating for the three nanogel dispersions onto $\text{bl-TiO}_2/\text{ITO}$ using SEM (see Fig. 2). Interestingly, individual NG-60 and NG-100 particles are not readily apparent. The NG-60 system showed nanosized films of ~ 1000 nm in diameter (Fig. 2a). Such features are due to localized nanogel coalescence and nanofilm formation. NG-100 also showed such nanofilms; however, they are smaller with a size of ~ 200 nm, which is indicative of localized coalescence with fewer nanogels coalesced per nanofilm (Fig. 2b). In contrast, NG-200 showed almost exclusively isolated particles (Fig. 2c) with only occasional limited inter-nanogel coalescence.

These trends arise because the average separation of the nanogels reduces with decreasing nanogel size at constant mass surface concentration (*i.e.*, nanogel mass per unit area). Furthermore, the likelihood of nanogel coalescence (and film formation) on a surface increases as the average interparticle separation decreases. Hence, nanofilm formation is more favorable at a concentration of 3.0 mg g^{-1} for NG-60 and NG-100, but less so for NG-200.

Morphology of perovskite films prepared using nanogels with different sizes

SEM images are shown for the perovskite films prepared with different nanogels (Fig. 3). Nanocrystals that grow vertically are

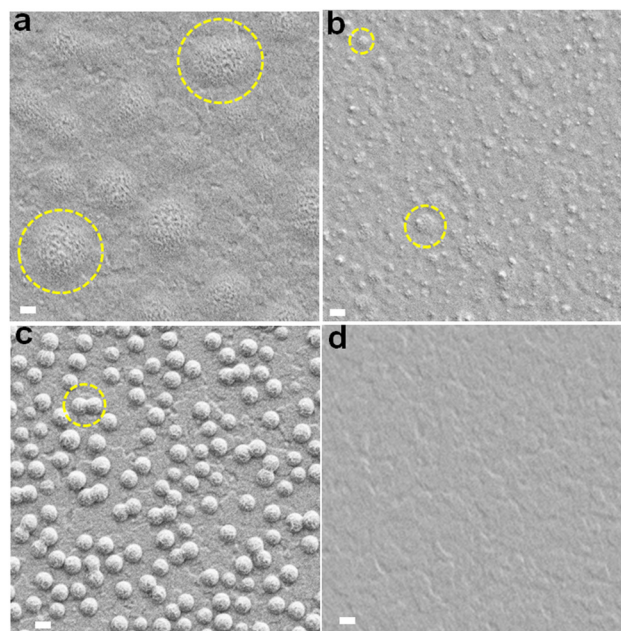


Fig. 2 SEM images ITO/ bl-TiO_2 substrates after spin-coating DMF/DMSO dispersions (3.0 mg g^{-1}) of (a) NG-60, (b) NG-100 and (c) NG-200 particles. An SEM of the bare ITO/ bl-TiO_2 substrate is shown in (d) for comparison. The yellow circles highlight coalesced nanogels. Scale bars: 200 nm.

apparent for some of the systems and we will discuss their origin below. The average grain size (Fig. S8, ESI[†]) decreased in the order NG-60 (1820 nm) > NG-100 (1625 nm) > CTRL (1375 nm) > NG-200 (1270 nm). As shown in the ESI[†] (Note 3), the estimated specific surface areas (A_s) of the NG-60, NG-100 and NG-200 particles are 165 , 103 and $34 \text{ m}^2 \text{ g}^{-1}$, respectively. Consequently, the nanogels have high surface areas available to bind to perovskite colloids that are present during crystallization. We conducted a crystallization rate experiment by following the change in the color of the films visually as a function of time during annealing (Fig. S9, ESI[†]). We used a nanogel concentration of 10 mg g^{-1} for this experiment to amplify the differences to enable clear visualization of the effect of nanogels on crystallization rate. (This produced some macroscopic particles which adversely affected compact perovskite structure formation and contributed to the decreased PCE for the 10 mg g^{-1} NG-100 system in Table S4 (ESI[†]).) The results show a significantly decreased crystallization rate in the presence of the nanogels. Such a decrease in the perovskite growth rate would increase the average grain sizes as shown by McMeekin *et al.*⁶⁸ Indeed, it is likely that nanogels binding with PbI_2 contributed to the decreased crystallization rate. In support of this proposal, DFT calculations of the charge transfer density (Fig. S10a, ESI[†]) and binding energies (Fig. S10b, ESI[†]) showed that PbI_2 interacts favorably with MEO_2MA monomer via Pb–O bonding.

Close examination of the SEM images of the perovskite/nanogel systems reveals that perovskite grains for the NG-60 system (Fig. 3a) are more rounded and have a less crystalline morphology compared to the control (Fig. 3d) as well as to



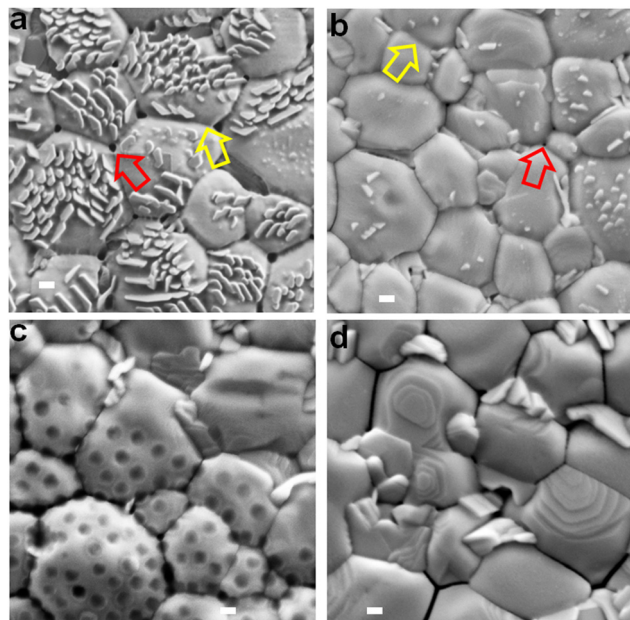


Fig. 3 Top view SEM images of the perovskite films prepared using (a) NG-60, (b) NG-100, (c) NG-200 and (d) the control without nanogels. The yellow arrows highlight nanofilm bridges between perovskite grains. The red arrows highlight small pinholes in the bridging nanofilms at the junction of three perovskite grains. Scale bars: 200 nm. See also Fig. S11 (ESI†).

those prepared with NG-100 (Fig. 3b) and NG-200 (Fig. 3c). Whilst individual NG-60 and NG-100 particles are absent, nanofilm segments can be seen bridging grains (yellow arrows). In contrast, the NG-200 system shows features due to NG-200 particles (Fig. 3c) with no evidence of nanofilms. NG-200 particles that bridge grains can also be seen. The control film shows large gaps between the grains (Fig. 3d). (These features are also shown in expanded SEM images in Fig. S11, ESI†.) Pinholes in the nanofilms are evident at the junctions of three grains (red arrows) in Fig. 3a and b, which are smallest for the NG-100 system. We conclude that nanofilms are present for the perovskites prepared with NG-60 and NG-100. In contrast, only individual nanogels (and not nanofilms) are present for perovskite/NG-200.

We were intrigued by the vertical nanocrystals and found that the NG-200 particles when used at 10 mg g^{-1} favor the growth of vertical nanocrystals adjacent to them (see Fig. S12, ESI†). It is likely that such a process also occurred for the smaller nanogels. Indeed, increasing the NG-100 concentration to greater than 3.0 mg g^{-1} increases the vertical nanocrystal surface concentration (Fig. S13, ESI†). Consequently, the surface concentration of vertical nanocrystals is an indirect measure of nanogel coverage. The link between vertical nanocrystals and nanogel coverage is discussed in more detail in the ESI† (Note 4). It follows from Fig. 3 that the nanogel film coverage was greatest for the NG-60 system and least for the NG-200 system. This suggestion was tested by conducting water contact angle measurements on the films (Fig. S14, ESI†). The nanogels are hydrophilic as discussed in the ESI† (Note 1). The contact angle for the perovskite films decreases in the order: CTRL > NG-200

> NG-100 > NG-60. Hence the surface becomes increasingly hydrophilic as the nanogel size decreases, which is attributed to greater coverage by nanogel nanofilms. This conclusion is congruent with the A_s calculations (Note 3, ESI†) wherein, the area of surface covered by a fixed nanogel mass concentration will increase in the order NG-200 < NG-100 < NG-60.

An interesting question concerns why a higher nanogel concentration is required to trigger vertical nanocrystal growth for NG-100 and NG-200 systems compared to NG-60. The concentration required to obtain a given coverage of the perovskite by the nanogels will increase as A_s decreases. A concentration of 3 mg g^{-1} for NG-60 ($A_s = 165 \text{ m}^2 \text{ g}^{-1}$) was required to produce a high surface concentration of vertical nanocrystals (Fig. 3a). However, perovskites prepared using 3 mg g^{-1} NG-100 ($A_s = 103 \text{ m}^2 \text{ g}^{-1}$) and NG-200 ($A_s = 34 \text{ m}^2 \text{ g}^{-1}$) had fewer vertical nanocrystals (Fig. 3b and c) due to less surface coverage by these nanogels. Accordingly, a higher nanogel concentration (e.g., 10 mg g^{-1}) was required for NG-100 and NG-200 to give sufficient surface coverages to trigger growth of high vertical nanocrystal concentrations (Fig. S12 and S13, ESI†).

Energy-dispersive X-ray (EDX) analysis was employed to analyze the composition of the vertical nanocrystals on the surface of perovskite films (Fig. S15, ESI†). A perovskite/NG-60 film (3 mg g^{-1}) was examined as well as the control film. Three distinct positions were scanned in each film. The corresponding elemental weight percentages at these positions are detailed in Table S5 (ESI†) as well as the Pb/I ratios. In the regions where only planar grains were analyzed (positions 1–3 of the control and positions 2 and 3 of the NG-60 sample), the Pb/I ratios were in the range of 0.64–0.86. This can be compared to the value expected of 0.56 based on the masses of PbI_2 , FAI and MAI used for $\text{FA}_{0.75}\text{MA}_{0.25}\text{PbI}_3$ synthesis. Hence, the planar grain surfaces are iodine-deficient. Iodide ions can easily diffuse due to their relatively low migration energy.^{14,69} Also, I_2 liberation at surfaces is well known for perovskites.^{70,71} Interestingly, a probe of the vertical nanocrystals (position 1 of Fig. S15(b), ESI†) gave a Pb/I ratio of 0.52, which is very close to that expected. This may indicate that the vertical nanocrystals are less susceptible to loss of I.

SEM cross-sectional images were also obtained for the films (Fig. S16, ESI†). The cross-sections for the NG-60 (Fig. S16a, ESI†) and NG-100 (Fig. S16b, ESI†) systems show many aligned amorphous grooves and undulations. In contrast, the NG-200 (Fig. S16c, ESI†) and control (Fig. S16d, ESI†) cross-sections show well-defined crystalline grains. Accordingly, the morphologies of the NG-60 and NG-100 perovskite fracture surfaces are indicative of plastic flow; whereas, those for the NG-200 and control films are typical of brittle fracture. To confirm this suggestion, we prepared a perovskite/NG-100 film using a nanogel concentration of 20 mg g^{-1} and obtained SEM cross-section images. A representative image (Fig. S17, ESI†) shows extensive plastic flow, due to a thicker NG-100 film. It is important to note that the inset from the cross-section (Fig. S17, ESI†) captures individual and coalesced NG-100 particles deep within the perovskite film between two grains. Hence, not only do these nanogels form nanofilms at the



perovskites surface, nanogels reside at grain boundaries in the perovskite interior.

Solar cell performance and stability

PSCs were constructed using a planar structure: glass/ITO/TiO₂/perovskite (nanogels)/Spiro-OMeTAD/Au (Fig. 4a). Box plots showing the measured device data appear in Fig. 4b. Photo-current density–voltage (*J*–*V*) curves for the best performing devices of each class are shown in Fig. 4c and the data are listed in Table S4 (ESI†). The overall best performing device is NG-100 with a champion PCE of 20.08%. This is almost 1.7% higher than the champion control device (18.40%). The best PCEs for the NG-60 (19.12%) and NG-200 (17.84%) systems are higher and lower, respectively, than the control device. Hence, both NG-100 and NG-60 improve the PCE of the PSCs; whereas, NG-200 decreases the PCE. Results from a literature survey shown in Table S6 (ESI†) reveal that the best PCE measured in this study is above average for comparable systems reported in the literature. Our devices were not designed for maximizing the PCE. We stress that the focus of this study is on passivation and stability in the model FA/MA system. Comprehensive studies on FA/MA/Cs or FA/Cs perovskites are planned for future detailed investigations. The data shown in Fig. 4b demonstrate that

variations of the open-circuit voltage (*V*_{oc}) and fill factor (FF) are primarily responsible for the PCE changes. Moreover, the data shown in Fig. S18 (ESI†) reveal that the average PCE measured during the reverse sweeps has a linear relationship with the product of the *V*_{oc} and (FF/100). Both of these quantities are increased by NG-60 and NG-100.

The EQE spectra (Fig. 4d) show that the integrated short-circuit current density (*J*_{sc}) values agree with those from the *J*–*V* curves to within 8%. The hysteresis index (Fig. S19 and Table S4, ESI†) is a minimum of 7.6% for the NG-100 system compared to 9.1% for the control. The average values for the NG-60 and NG-200 devices are 12.7% and 9.8%, respectively. Hence, these results suggest that NG-100 is better able to oppose the build-up of mobile ions that are the major contributor to hysteresis in PSCs.⁷²

Light intensity variation against *V*_{oc} data were measured (Fig. 4e) and analyzed to investigate charge recombination behavior. The ideality factor (*n*) is calculated using eqn (1),⁷³

$$n = \frac{q}{kT} \frac{dV_{oc}}{d \log I} \quad (1)$$

where *q*, *k*, *T*, and *I* are charge of the electron, Boltzmann constant, temperature and intensity of incident light,

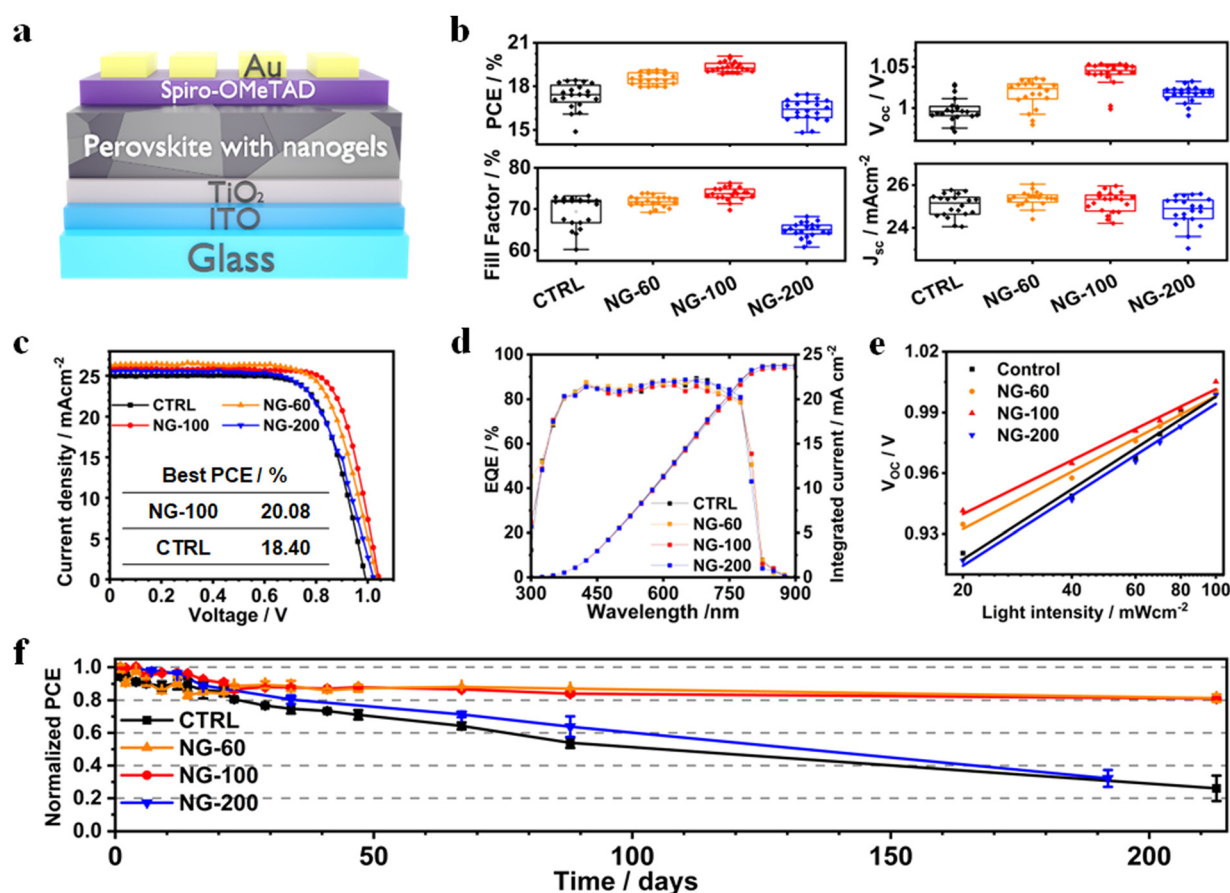


Fig. 4 (a) Device architecture used. (b) Measured PCEs, fill factors, open-circuit voltages and short-circuit current densities for the devices. (c) *J*–*V* curves for selected devices. (d) EQE data for the devices. (e) The variation of the open-circuit voltage with incident light intensity. (f) Normalized PCE shelf-life storage data for the PSCs. The unencapsulated devices were stored at room temperature in the dark under ambient conditions, RH = 35%.



respectively. The n value is 1.95 for the control system; whereas, it is 1.49, 1.59 and 1.93 for NG-100, NG-60 and NG-200 system, respectively. A lower n value indicates that the trap-assisted recombination is less dominant.⁷⁴ Hence, the NG-100 and NG-60 systems are most effective at decreasing trap-assisted recombination. As shown in Fig. S20 (ESI†), there is a correlation between the measured J_{sc} and light intensity, following the relationship:⁷⁵ $J_{sc} \propto I^\alpha$. The α value for NG-100 (0.97) and NG-60 (0.97) is closer to unity than the control (0.95) and NG-200 (0.96), suggesting a decrease in bimolecular recombination.⁷⁶

Space-charge-limited current (SCLC) tests were performed to analyse the trap density in the perovskite films using electron-only (ITO/TiO₂/perovskite/PC₆₁BM/Au) devices. Fig. S21 (ESI†) shows the dark current–voltage characteristics of various devices and the trap-filled limit voltage (V_{TFL}) values. The calculation of trap density used⁷⁷

$$N_t = \frac{2\epsilon\epsilon_0 V_{TFL}}{qL^2} \quad (2)$$

where ϵ and ϵ_0 are the relative dielectric constant of perovskite (which is 46.9⁷⁸) and the vacuum dielectric constant,⁷⁹ respectively. The parameter L is the perovskite film thickness, and these values were measured from Fig. S16 (ESI†). Accordingly, the trap densities for the control, NG-60, NG-100 and NG-200 systems are $1.$

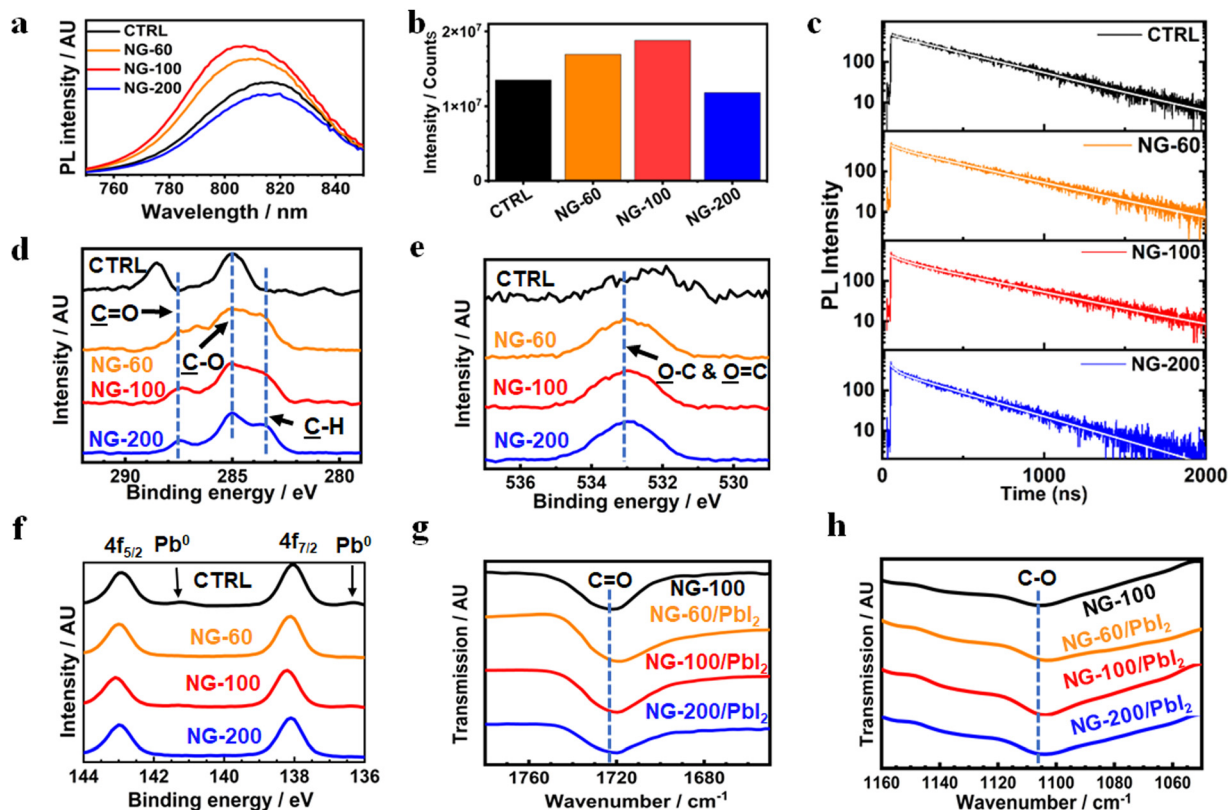


Fig. 5 (a) PL spectra for various perovskite/nanogel systems. (b) The maximum PL intensity from the spectra in (a). (c) TRPL data for various perovskite films. (d) C 1s, (e) O 1s and (f) Pb 4f core level spectra from XPS measurements for the control perovskite and films prepared with nanogels (3 mg g⁻¹). (g) C

- 52 A. H. Milani, J. M. Saunders, N. T. Nguyen, L. P. D. Ratcliffe, D. J. Adlam, A. J. Freemont, J. A. Hoyland, S. P. Armes and B. R. Saunders, *Soft Matter*, 2017, **13**, 1554–1560.
- 53 O. M. Alkhudhari, A. Altujjar, M. Z. Mokhtar, B. F. Spencer, Q. Chen, A. G. Thomas, N. W. Hodson, X. Wang, P. Hill, J. Jacobs, R. J. Curry and B. R. Saunders, *J. Mater. Chem. A*, 2022, **10**, 10227–10241.
- 54 O. M. Alkhudhari, R. Wang, Z. Jia, N. W. Hodson, A. Alruwaili, A. Altujjar, E. Picheo and B. R. Saunders, *RSC Adv.*, 2024, **14**, 6190–6198.
- 55 A. Altujjar, M. Z. Mokhtar, Q. Chen, J. Neilson, B. F. Spencer, A. Thomas, J. M. Saunders, R. Wang, O. Alkhudhari, A. Mironov and B. R. Saunders, *ACS Appl. Mater. Interfaces*, 2021, **13**, 58640–58651.
- 56 D. Portoghesi and A. F. Routh, *Chem. Eng. Res. Des.*, 2005, **83**, 139–142.
- 57 A. Toussaint and M. De Wilde, *Prog. Org. Coat.*, 1997, **30**, 113–126.
- 58 E. Buratti, I. Sanzari, F. Dinelli, T. Prodromakis and M. Bertoldo, *Polymers*, 2020, **12**, 2638.
- 59 D. Saatweber and B. Vogt-Birnbrich, *Prog. Org. Coat.*, 1996, **28**, 33–41.
- 60 J. Engström, C. J. Brett, V. Körstgens, P. Müller-Buschbaum, W. Ohm, E. Malmström and S. V. Roth, *Adv. Funct. Mater.*, 2020, **30**, 1907720.
- 61 S. Galindo, A. Tamayo, F. Leonardi and M. Mas-Torrent, *Adv. Funct. Mater.*, 2017, **27**, 1700526.
- 62 M.-B. Madec, J. J. Morrison, V. Sanchez-Romaguera, M. L. Turner and S. G. Yeates, *J. Mater. Chem.*, 2009, **19**, 6750–6755.
- 63 A. Campos, S. Riera-Galindo, J. Puigdollers and M. Mas-Torrent, *ACS Appl. Mater. Interfaces*, 2018, **10**, 15952–15961.
- 64 H. Bachman, A. C. Brown, K. C. Clarke, K. S. Dhada, A. Douglas, C. E. Hansen, E. Herman, J. S. Hyatt, P. Kodlekere, Z. Meng, S. Saxena, M. W. Spears Jr, N. Welsch and L. A. Lyon, *Soft Matter*, 2015, **11**, 2018–2028.
- 65 B. Chen, P. N. Rudd, S. Yang, Y. Yuan and J. Huang, *Chem. Soc. Rev.*, 2019, **48**, 3842–3867.
- 66 M. Abdi-Jalebi, Z. Andaji-Garmaroudi, S. Cacovich, C. Stavarakas, B. Philippe, J. M. Richter, M. Alsari, E. P. Booker, E. M. Hutter, A. J. Pearson, S. Lilliu, T. J. Savenije, H. Rensmo, G. Divitini, C. Ducati, R. H. Friend and S. D. Stranks, *Nature*, 2018, **555**, 497–501.
- 67 J. Xue, R. Wang and Y. Yang, *Nat. Rev. Mater.*, 2020, **5**, 809–827.
- 68 D. P. McMeekin, Z. Wang, W. Rehman, F. Pulvirenti, J. B. Patel, N. K. Noel, M. B. Johnston, S. R. Marder, L. M. Herz and H. J. Snaith, *Adv. Mater.*, 2017, **29**, 1607039.
- 69 D. W. Ferdani, S. R. Pering, D. Ghosh, P. Kubiak, A. B. Walker, S. E. Lewis, A. L. Johnson, P. J. Baker, M. S. Islam and P. J. Cameron, *Energy Environ. Sci.*, 2019, **12**, 2264–2272.
- 70 S. Wang, Y. Jiang, E. J. Juarez-Perez, L. K. Ono and Y. Qi, *Nat. Energy*, 2016, **2**, 16195.
- 71 T. Webb and S. A. Haque, *Energy Environ. Sci.*, 2024, **17**, 3244–3269.
- 72 G. Tumen-Ulzii, T. Matsushima, D. Klotz, M. R. Leyden, P. Wang, C. Qin, J.-W. Lee, S.-J. Lee, Y. Yang and C. Adachi, *Commun. Mater.*, 2020, **1**, 31.
- 73 A. Mahapatra, N. Parikh, P. Kumar, M. Kumar, D. Prochowicz, A. Kalam, M. M. Tavakoli and P. Yadav, *Molecules*, 2020, **25**, 2299.
- 74 L. Xie, S. Du, J. Li, C. Liu, Z. Pu, X. Tong, J. Liu, Y. Wang, Y. Meng, M. Yang, W. Li and Z. Ge, *Energy Environ. Sci.*, 2023, **16**, 5423–5433.
- 75 V. D. Mihailitchi, H. X. Xie, B. de Boer, L. J. A. Koster and P. W. M. Blom, *Adv. Funct. Mater.*, 2006, **16**, 699–708.
- 76 L. Liu, C. Zheng, Z. Xu, Y. Li, Y. Cao, T. Yang, H. Zhang, Q. Wang, Z. Liu, N. Yuan, J. Ding, D. Wang and S. Liu, *Adv. Energy Mater.*, 2023, **13**, 2300610.
- 77 Y. Huang, L. Li, Z. Liu, H. Jiao, Y. He, X. Wang, R. Zhu, D. Wang, J. Sun, Q. Chen and H. Zhou, *J. Mater. Chem. A*, 2017, **5**, 8537–8544.
- 78 Q. Han, S.-H. Bae, P. Sun, Y.-T. Hsieh, Y. Yang, Y. S. Rim, H. Zhao, Q. Chen, W. Shi, G. Li and Y. Yang, *Adv. Mater.*, 2016, **28**, 2253–2258.
- 79 H. Min, M. Kim, S.-U. Lee, H. Kim, G. Kim, K. Choi, J. H. Lee and S. I. Seok, *Science*, 2019, **366**, 749–753.
- 80 A. Marchioro, J. Teuscher, D. Friedrich, M. Kunst, R. van de Krol, T. Moehl, M. Grätzel and J.-E. Moser, *Nat. Photonics*, 2014, **8**, 250–255.
- 81 R. J. E. Westbrook, T. J. Macdonald, W. Xu, L. Lanzetta, J. M. Marin-Beloqui, T. M. Clarke and S. A. Haque, *J. Am. Chem. Soc.*, 2021, **143**, 12230–12243.
- 82 T. Webb, X. Liu, R. J. E. Westbrook, S. Kern, M. T. Sajjad, S. Jenatsch, K. D. G. I. Jayawardena, W. H. K. Perera, I. P. Marko, S. Sathasivam, B. Li, M. Yavari, D. J. Scurr, M. R. Alexander, T. J. Macdonald, S. A. Haque, S. J. Sweeney and W. Zhang, *Adv. Energy Mater.*, 2022, **12**, 2200666.
- 83 F. T. F. O'Mahony, Y. H. Lee, C. Jellett, S. Dmitrov, D. T. J. Bryant, J. R. Durrant, B. C. O'Regan, M. Graetzel, M. K. Nazeeruddin and S. A. Haque, *J. Mater. Chem. A*, 2015, **3**, 7219–7223.
- 84 Z. Xu, Z. Liu, N. Li, G. Tang, G. Zheng, C. Zhu, Y. Chen, L. Wang, Y. Huang, L. Li, N. Zhou, J. Hong, Q. Chen and H. Zhou, *Adv. Mater.*, 2019, **31**, 1900390.
- 85 M. Salado, A. D. Jodlowski, C. Roldan-Carmona, G. de Miguel, S. Kazim, M. K. Nazeeruddin and S. Ahmad, *Nano Energy*, 2018, **50**, 220–228.
- 86 Z. Wu, M. Jiang, Z. Liu, A. Jamshaid, L. K. Ono and Y. Qi, *Adv. Energy Mater.*, 2020, **10**, 1903696.
- 87 *Principles of Fluorescence Spectroscopy*, ed. J. R. Lakowicz, Springer US, Boston, MA, 2006, pp. 27–61.
- 88 W. Zhao, H. Lin, Y. Li, D. Wang, J. Wang, Z. Liu, N. Yuan, J. Ding, Q. Wang and S. Liu, *Adv. Funct. Mater.*, 2022, **32**, 2112032.
- 89 F. Li, X. Deng, F. Qi, Z. Li, D. Liu, D. Shen, M. Qin, S. Wu, F. Lin, S.-H. Jang, J. Zhang, X. Lu, D. Lei, C.-S. Lee, Z. Zhu and A. K. Y. Jen, *J. Am. Chem. Soc.*, 2020, **142**, 20134–20142.
- 90 Q. An, F. Paulus, D. Becker-Koch, C. Cho, Q. Sun, A. Weu, S. Bitton, N. Tessler and Y. Vaynzof, *Matter*, 2021, **4**, 1683–1701.



- 91 Y. Chang, C.-Y. Ko, Y.-J. Shih, D. Quémener, A. Deratani, T.-C. Wei, D.-M. Wang and J.-Y. Lai, *J. Membr. Sci.*, 2009, **345**, 160–169.
- 92 L. Islas, J.-C. Ruiz, F. Muñoz-Muñoz, T. Isoshima and G. Burillo, *Appl. Surf. Sci.*, 2016, **384**, 135–142.
- 93 F. Zhang, E. T. Kang, K. G. Neoh, P. Wang and K. L. Tan, *Biomaterials*, 2001, **22**, 1541–1548.
- 94 J. Guo, B. Wang, D. Lu, T. Wang, T. Liu, R. Wang, X. Dong, T. Zhou, N. Zheng, Q. Fu, Z. Xie, X. Wan, G. Xing, Y. Chen and Y. Liu, *Adv. Mater.*, 2023, **35**, 2212126.
- 95 T. Zhu, L. Shen, S. Xun, J. S. Sarmiento, Y. Yang, L. Zheng, H. Li, H. Wang, J.-L. Bredas and X. Gong, *Adv. Mater.*, 2022, **34**, 2109348.
- 96 C. Ma and N.-G. Park, *ACS Energy Lett.*, 2020, **5**, 3268–3275.

