



Cite this: *Phys. Chem. Chem. Phys.*,
2024, 26, 15332

Direct reduction of NO into N₂ catalyzed by fullerene-supported rhodium clusters†

Ruomeng Li, Ya-Ke Li,* Jianzhi Xu  and Gao-Lei Hou *

Catalytic conversion of NO has long been a focus of atmospheric pollution control and diesel vehicle exhaust treatment. Rhodium is one of the most effective metals for catalyzing NO reduction, and understanding the nature of the active sites and underlying mechanisms can help improve the design of Rh-based catalysts towards NO reduction. In this work, we investigated the detailed catalytic mechanisms for the direct reduction of NO to N₂ by fullerene-supported rhodium clusters, C₆₀Rh₄⁺, with density functional theory calculations. We found that the presence of C₆₀ facilitates the smooth reduction of NO into N₂ and O₂, as well as their subsequent desorption, recovering the catalyst C₆₀Rh₄⁺. Such a process fails to be completed by free Rh₄⁺, emphasizing the critical importance of C₆₀ support. We attribute the novel performance of C₆₀Rh₄⁺ to the electron sponge effect of C₆₀, providing useful guidance for designing efficient catalysts for the direct reduction of NO.

Received 5th April 2024,
Accepted 2nd May 2024

DOI: 10.1039/d4cp01398k

rsc.li/pccp

Introduction

Nitric oxide (NO) is an air pollutant associated with severe environmental issues, posing great health risks to human beings. Its treatment has received extensive efforts,^{1,2} and current methods for NO control, such as absorption, decomposition, and reduction, always encounter shortcomings such as process complexity and by-product generation.³ The three-way catalyst (TWC), which employs noble metals such as Pt, Pd, and Rh, stands out as an effective catalyst for reducing NO emissions in automobile exhaust. In particular, rhodium excels in NO chemical adsorption and dissociation, showing great activity and selectivity in NO reduction into N₂.^{4,5}

Previous studies investigated the dissociation and adsorption of NO on the surfaces of Rh(100), Rh(111), and Rh(110) surfaces and found that N atoms bind and desorb at 450–650 K, and O atoms desorb in O₂ form at 1000–1400 K.^{6–18} It is shown that Rh-doped metal catalysts exhibit more superior catalytic performance than pure metal catalysts for converting NO, emphasizing the critical importance of rhodium.^{19,20} However, rhodium is scarce and expensive, limiting its widespread utilization.^{1,3,4} In this regard, recently emerged single-atom catalysts (SACs) and single-cluster catalysts (SCCs) that offer high atomic efficiency^{21–23} may provide an interesting approach for employing Rh-based catalysts in NO conversion.

Mass spectrometric experiments and theoretical calculations on the reactions of free rhodium clusters with NO have elucidated the important role of Rh in N–O bond activation.^{24–33} For instance, Ghosh *et al.* found that Rh clusters containing one to five atoms exhibit stronger bonding with NO compared to Rh(100) and Rh(111), rendering Rh clusters to be good catalysts for NO reduction.²⁵ Xie *et al.* studied the NO adsorption and reduction on the Rh₇⁺ cluster and found that the reaction follows a three-step process: initial adsorption of NO, subsequent NO decomposition into N and O atoms, and then, the reaction of the N atom with a second adsorbed NO, leading to the formation of N₂ molecules and rhodium oxides.²⁷ Romo-Ávila *et al.* investigated the NO dissociation on Rh_{*n*}[±] clusters (*n* = 3, 4, 6, and 13) and found that the dissociation of N–O is more feasible on square facets than on triangular atomic environments.²⁸ They also found the energy barrier for breaking the N–O bond depends on the charge states of the rhodium clusters, with cationic clusters being more reactive than neutrals and anions, in agreement with an earlier experimental study.²⁴

Previously, Mackenzie and co-workers found that once two NO molecules co-adsorb on Rh_{*x*}[±] clusters, NO first dissociates to generate mobile N atoms that can then combine to form N₂ molecules; resultant rhodium dioxide clusters Rh_{*x*}O₂[±] further adsorb NO, and the process of NO reduction to N₂ replicates, yielding higher rhodium oxides.²⁴ In these cases, catalytic reactions stopped with the formation of rhodium oxides and no O₂ release, that will, in the end, lead to the deactivation of the catalysts.^{24,26,27,31,33} Then, a question arises: if a catalytic cycle cannot be completed on free rhodium clusters, how about when supported on certain substrates, considering that in practice most metal catalysts are dispersed on supports like

MOE Key Laboratory for Non-Equilibrium Synthesis and Modulation of Condensed Matter, School of Physics, Xi'an Jiaotong University, Xi'an, 710049 Shaanxi, China.
E-mail: yake.li@xjtu.edu.cn, gaolei.hou@xjtu.edu.cn

† Electronic supplementary information (ESI) available: calculated isomers of Rh₄⁺, C₆₀Rh₄⁺, and C₆₀Rh⁺; additional reaction pathways; calculated NBO partial charges; cartesian coordinates. See DOI: <https://doi.org/10.1039/d4cp01398k>

metal oxides and porous carbon materials? In this regard, Chen *et al.* recently showed that Rh-doped anionic clusters, $\text{RhCe}_2\text{O}_{3-5}^-$, with Rh acting as the “active center” and $\text{Ce}_2\text{O}_{3-5}$ as the “support”, can effectively prompt NO reduction into N_2 by introducing CO molecules.³⁴

In this work, we report the study on the reduction of NO to N_2 catalyzed by $\text{C}_{60}\text{Rh}_4^+$ clusters, with those by free Rh_4^+ and C_{60}Rh^+ clusters as comparison. These clusters were chosen because (i) German *et al.* recently investigated the structures of $\text{C}_{60}\text{Rh}_n^+$ ($n = 1-6$) clusters using infrared multiple photon dissociation spectroscopy and found that $\text{C}_{60}\text{Rh}_4^+$ has a square Rh_4^+ moiety, different from the pyramidal structure for free Rh_4^+ ,³⁵ while square Rh_4^+ has been shown to be more reactive for N–O dissociation than a triangular one²⁸ and (ii) C_{60} has been shown to have a novel geometric and electronic effect in promoting catalytic reactions.³⁶⁻³⁹ We find that it is more energetically favorable for $\text{C}_{60}\text{Rh}_4^+$ than C_{60}Rh^+ in catalyzing NO conversion, and the presence of C_{60} promotes O_2 desorption, allowing the completion of the reaction cycle. We aim to gain insights into the nature of catalytic active sites and reaction mechanisms to guide the improvement of Rh-based catalysts for NO reduction.

Theoretical methods

All DFT calculations were carried out using the Gaussian 09 program⁴⁰ package to investigate the structures of Rh_4^+ , C_{60}Rh^+ , and $\text{C}_{60}\text{Rh}_4^+$ and their reaction mechanisms with NO. Three functionals, BPW91,^{41,42} PBE,⁴³ and B3LYP,^{44,45} were tested for optimizing the structures of Rh_4^+ , C_{60}Rh^+ , and $\text{C}_{60}\text{Rh}_4^+$. The 6-31G(d) basis set was used for N, O, and C, and the SDD⁴⁶ basis set for Rh. It was found that PBE and BPW91 could well reproduce the structures of C_{60}Rh^+ and $\text{C}_{60}\text{Rh}_4^+$ determined previously (see Fig. S1–S4 in ESI†).³⁵ Since BPW91 has been found to be superior in simulating the infrared spectra of fullerene-metal clusters in terms of efficiency and accuracy,^{36,37,47,48} it was chosen to optimize all the geometries of transition states and intermediates

during the catalytic NO conversion process. Harmonic frequency analysis was performed to make sure all transition states have only one imaginary frequency and the intermediates have none. Intrinsic reaction coordinate (IRC) calculations were conducted to validate the calculated transition state structures and to confirm the nature and stability of reaction pathways.⁴⁹ The natural bond orbital (NBO) analysis was performed with NBO 3.1 as implemented in Gaussian 09.⁵⁰

Results and discussion

We first confirm that BPW91 can provide reliable structures for Rh_4^+ , C_{60}Rh^+ , and $\text{C}_{60}\text{Rh}_4^+$ as determined from previous experiments (see Fig. S1–S4 in ESI†).³⁵ The most stable structure of $\text{C}_{60}\text{Rh}_4^+$ has a quartet state with the four Rh atoms adsorbed on one hexagonal surface of fullerene, forming a square shape parallel to the hexagon, as shown in Fig. 1. The adsorbed NO molecule binds with $\text{C}_{60}\text{Rh}_4^+$ through a Rh–N bond due to the high affinity of small rhodium clusters towards N atoms.^{20,25} This step forms the first intermediate IN1 with an exothermic energy of $55.7 \text{ kcal mol}^{-1}$, smaller than the calculated binding energy of $88.8 \text{ kcal mol}^{-1}$ between C_{60} and Rh_4^+ in $\text{C}_{60}\text{Rh}_4^+$. Subsequently, the N–O bond undergoes dissociation, which is facilitated by the two adjacent Rh atoms. The energy barrier associated with this process is $49.6 \text{ kcal mol}^{-1}$, resulting in the formation of a Rh–N bond and a Rh–O bond in IN2 ($\text{IN1} \rightarrow \text{TS1}$). Then, a second NO molecule adsorbs on IN2, resulting in the formation of the intermediate IN3 *via* forming another Rh–N bond. This process exothermically releases an energy of $55.8 \text{ kcal mol}^{-1}$, similar to the energy released by the first NO adsorption. Then, the N–O bond is cleaved by the other two adjacent Rh atoms. Thereafter, all four Rh sites are fully occupied by two N atoms and two O atoms ($\text{IN3} \rightarrow \text{TS2} \rightarrow \text{IN4}$). The energy barrier for this process is $56.8 \text{ kcal mol}^{-1}$, about 7 kcal mol^{-1} higher than the first N–O bond dissociation, presumably due to the steric effect of the pre-adsorbed N and O

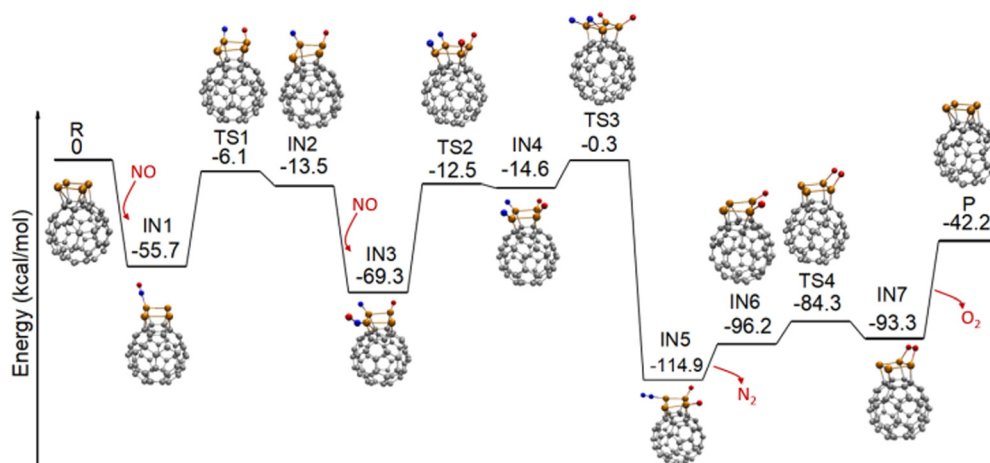


Fig. 1 Reaction pathway of NO reduction on $\text{C}_{60}\text{Rh}_4^+$ calculated at the BPW91/6-31G(d)&SDD level of theory. R stands for reactants, IN for intermediates, TS for transition states, and P for products. All energies are provided relative to the energies of the reactants, *i.e.*, $\text{C}_{60}\text{Rh}_4^+$ and two NO molecules.

atoms from the first NO molecule. This process behaves as the rate-determining step in the catalytic NO reduction by the $C_{60}Rh_4^+$ cluster.

Upon combination of the two dissociated nitrogen atoms on the “surface” of the rhodium cluster by overcoming a barrier of $14.3 \text{ kcal mol}^{-1}$, the N_2 moiety forms in a very stable intermediate IN5 that is $114.9 \text{ kcal mol}^{-1}$ below the energy of the reactants. Subsequently, N_2 desorbs from the cluster with an endothermic energy of $18.7 \text{ kcal mol}^{-1}$, forming the intermediate IN6 (IN4 \rightarrow TS3 \rightarrow IN5 \rightarrow IN6). Then, the two O atoms on the “surface” of the rhodium cluster interact with each other to form an O_2 moiety in IN7 through a barrier of $11.9 \text{ kcal mol}^{-1}$ (IN6 \rightarrow TS4 \rightarrow IN7). Afterwards, the O_2 molecule desorbs by adsorbing an energy of $51.1 \text{ kcal mol}^{-1}$, completing a reaction cycle for the direct reduction of NO to N_2 catalyzed by $C_{60}Rh_4^+$, *i.e.*, $NO + NO \xrightarrow{C_{60}Rh_4^+} N_2 + O_2$. Overall, the calculation shows that this reaction has an exothermic energy of $42.2 \text{ kcal mol}^{-1}$, in excellent agreement with the experimental value of $41.4 \text{ kcal mol}^{-1}$.³ During the reaction, the four Rh atoms serve as the active sites for the activation and conversion of two NO molecules.

To elucidate the important role of multiple Rh sites for NO reduction, we calculate the reaction pathway of two NO molecules reacting with a C_{60} -fullerene-supported single rhodium atom, *i.e.*, $C_{60}Rh^+$ (see Fig. S5, ESI[†]). It seems that although the reaction cycle can be completed, first and second N–O bond dissociations encounter significant energy barriers, amounting to 103.2 and $89.7 \text{ kcal mol}^{-1}$, respectively. Such barriers are even larger than the calculated binding energy of $82.3 \text{ kcal mol}^{-1}$ between C_{60} and Rh^+ in $C_{60}Rh^+$,³⁵ which may result in the destruction of the $C_{60}Rh^+$ cluster first before the reaction can proceed, precluding its usefulness in practice.

The above discussion raises an interesting question: What is the role of C_{60} in the reaction? Can the same reaction cycle be completed without the presence of C_{60} ? To answer these questions, we investigated the adsorption and dissociation pathway of two NO molecules on a free Rh_4^+ cluster and presented it in Fig. 2. The most stable structure of Rh_4^+ is a pyramid with a doublet state. The first NO molecule is adsorbed on Rh_4^+ through a Rh–N

bond, forming the intermediate IN1 with an energy release of $62.1 \text{ kcal mol}^{-1}$. Subsequently, the N–O bond undergoes dissociation facilitated by two adjacent Rh sites, resulting in the formation of a Rh–O bond and a Rh–N–Rh ring in IN2 (IN1 \rightarrow TS1 \rightarrow IN2). The energy barrier for this process is calculated to be $29.2 \text{ kcal mol}^{-1}$, consistent with the calculated value of $27.7 \text{ kcal mol}^{-1}$ for N–O bond dissociation of NO on Rh_4^+ reported by Romo-Ávila *et al.*²⁸ Then, the cluster adsorbs a second NO molecule, forming a very stable intermediate, IN3, which is about $130 \text{ kcal mol}^{-1}$ below the total energy of reactants and releases an energy of $68.3 \text{ kcal mol}^{-1}$. Similar to the first NO dissociation, a second Rh–N–Rh ring and a Rh–O–Rh ring form in IN4 *via* TS2. The barrier for this step is $55.4 \text{ kcal mol}^{-1}$, in agreement with the value of $57.7 \text{ kcal mol}^{-1}$ reported for the second N–O bond dissociation.²⁷ This step is the rate-determining step in the reaction of NO molecules with the Rh_4^+ cluster.

In the following process, the two N atoms on the cluster surface migrate and encounter each other to combine to form a N_2 moiety by overcoming an energy barrier of $39.8 \text{ kcal mol}^{-1}$ (IN4 \rightarrow TS3 \rightarrow IN5). Subsequently, N_2 desorbs from the cluster surface by absorbing $15.6 \text{ kcal mol}^{-1}$ energy, resulting in the formation of the product $Rh_4O_2^+$ (IN5 \rightarrow TS4 \rightarrow IN6 \rightarrow P). Our calculated results on the reaction of Rh_4^+ with NO match the previous theoretical results on the reaction between NO and Rh_n^+ ($n = 4, 6, \text{ or } 7$) clusters.^{26–28} However, due to the geometric constraint, as the two O atoms in $Rh_4O_2^+$ are spatially distant, the combination of the two O atoms to form O_2 is hindered at normal temperatures. For example, Torres *et al.* calculated the desorption energy of O_2 from $Rh_6O_2^+$, *i.e.*, $\Delta E = E(Rh_6^+) + E(O_2) - E(Rh_6^+O_2)$, to be approximately 3.07 eV ($70.8 \text{ kcal mol}^{-1}$), almost 20 kcal mol^{-1} higher than that in the presence of C_{60} .²⁶ Such a process is expected to occur only at high temperatures, for instance, in the range of $1000\text{--}1400 \text{ K}$.¹⁸ These analyses highlight the unique role of C_{60} in facilitating the completion of the reaction cycle of $NO + NO \rightarrow N_2 + O_2$.

To more properly uncover the geometric effect and electronic effect when comparing the catalytic performance of $C_{60}Rh_4^+$ and Rh_4^+ , we also calculated the reaction pathway of NO reduction on square Rh_4^+ , a less stable isomer for the Rh_4^+

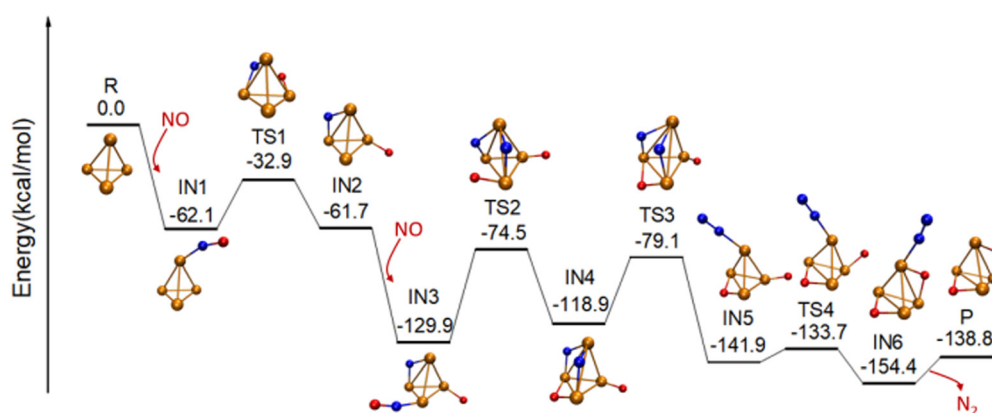


Fig. 2 Reaction pathway of NO reduction on Rh_4^+ calculated at the BPW91/6-31G(d)θSDD level of theory. R stands for reactants, IN for intermediates, TS for transition states, and P for products. All energies are provided relative to the energies of the reactants, *i.e.*, Rh_4^+ and two NO molecules.

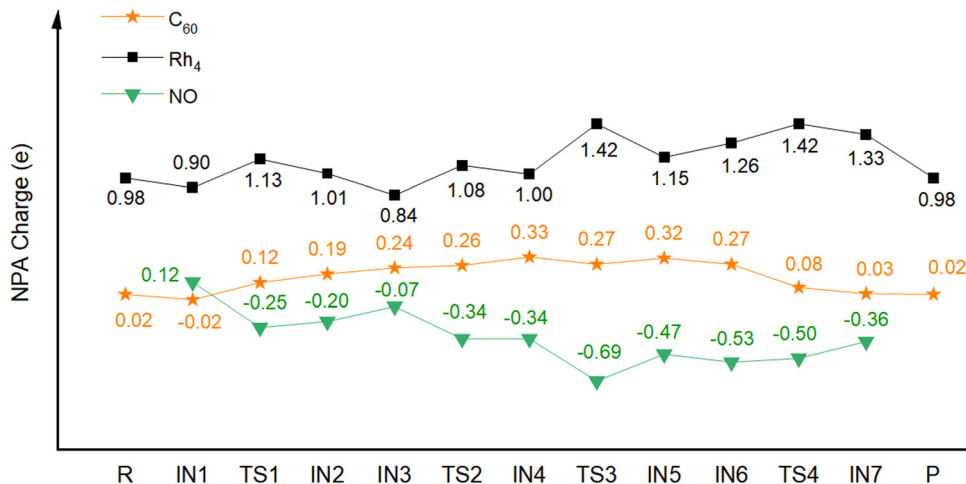


Fig. 3 Calculated NBO partial charges (e) of the Rh_4^+ cluster (black square) and C_{60} (orange star) of NO reduction catalyzed by $\text{C}_{60}\text{Rh}_4^+$.

cluster but possessing a similar geometry of the Rh_4^+ moiety in $\text{C}_{60}\text{Rh}_4^+$. Fig. S6 in the ESI† presents the result, and it can be seen that although it seems the NO reduction into N_2 and O_2 on square Rh_4^+ can be fulfilled, the energy barriers for the two-NO-bond cleavage are 54.5 and 61.6 kcal mol⁻¹, both about 5 kcal mol⁻¹ higher than the barriers on $\text{C}_{60}\text{Rh}_4^+$. This clearly shows that the electronic effect is in play. Overall, both geometric and electronic effects play roles in the catalytic NO reduction by $\text{C}_{60}\text{Rh}_4^+$, as the most stable Rh_4^+ becomes square from pyramidal when it is supported on C_{60} , demonstrating the important support effect.

To uncover why C_{60} can have such a role in the catalytic reduction of NO to N_2 , we conducted natural bond orbital (NBO) analysis. Fig. 3 shows the calculated NBO partial charges of the Rh_4^+ moiety and C_{60} of NO reduction catalyzed by $\text{C}_{60}\text{Rh}_4^+$, and the charge changes for the catalytic reactions of NO by pyramid Rh_4^+ , square Rh_4^+ and $\text{C}_{60}\text{Rh}_4^+$ are shown in Fig. S7–S9 (ESI†), respectively. It can be seen that the metal moiety shows alternating charges increasing and decreasing due to the cooperative effect of the electrophilic reactant NO, its dissociated N and O atoms, and the C_{60} support. Before the formation of IN4, the C_{60} support progressively donates electrons to metal and the reactant and reaches a maximum positive charge of 0.33 e; afterwards, before releasing the N_2 molecule (IN6), the charges on Rh_4 and C_{60} show exactly reverse trends; then, the positive charge on C_{60} keeps decreasing, meaning that C_{60} has been accepting electrons from metal and/or the reactant. Thus, during the whole process, C_{60} alternatively donates and accepts electrons, behaving as an “electron sponge”, as we previously proposed.^{37,38} Specifically, for the O_2 desorption process, the charge changes seem to reduce the interaction between Rh_4^+ and O atoms and simultaneously increase the binding energy between Rh_4^+ and C_{60} . Hence, the presence of C_{60} enables the O atoms to become “surface” O rather than “lattice” O, making the desorption of the O_2 molecule easier. In the case of free Rh_4^+ , the reactant seems to extract electrons from metal due to their higher electron negativity compared to metal, thus increasing the binding strength between metal and reactant. Without the electronic buffering effect of C_{60} , such an enhanced

binding strength would make desorption of the formed molecules difficult.

Conclusions

In summary, we studied the catalytic NO reduction into N_2 by rhodium clusters, in particular Rh_4^+ , with and without the presence of C_{60} -fullerene support. The Rh atoms serve as the active sites for the reduction of two NO molecules, and the C_{60} support plays an important role in regenerating the Rh_4^+ catalyst with relatively smooth O_2 desorption, which is difficult for free Rh_4^+ without the presence of C_{60} as it forms a stable rhodium oxide cluster, Rh_4O_2^+ . The introduction of C_{60} support not only induces a geometric transformation for the ground state of free Rh_4^+ from a trigonal pyramid to a square form but also can donate to or accept from the metal electrons during the NO catalytic reduction. This work demonstrates the electron sponge behavior of C_{60} , and the ability of C_{60} to donate and accept charges at distinct steps within the reaction between NO and Rh clusters sheds light on the intricate electronic interactions involved, offering valuable insights for designing efficient catalysts in the realm of direct reduction of NO.

Author contributions

G.-L. H. conceived and designed the research. R. L., Y.-K. L., and J. X. performed the research. R. L., Y.-L., and G.-L. H. wrote the manuscript. All authors approved the final version of the manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by the National Natural Science Foundation of China (92261101), Innovation Capability

Support Program of Shaanxi Province (2023-CX-TD-49), and Research Foundation–Flanders FWO (G033724N). G.-L. H. acknowledges the support from the Fundamental Research Funds for Central Universities, China. Part of the computational resources and services used in this work were provided by the VSC (Flemish Supercomputer Center), funded by the Research Foundation–Flanders (FWO) and Flemish Government–Department EWI.

Notes and references

- H. Gandhi, G. Graham and R. W. McCabe, *J. Catal.*, 2003, **216**, 433–442.
- J. M. Bakker and F. Mafuné, *Phys. Chem. Chem. Phys.*, 2022, **24**, 7595–7610.
- S. Roy, M. Hegde and G. Madras, *Appl. Energy*, 2009, **86**, 2283–2297.
- K. C. Taylor, *Catal. Rev.*, 1993, **35**, 457–481.
- M. Shelef and G. Graham, *Catal. Rev.*, 1994, **36**, 433–457.
- R. Baird, R. Ku and P. Wynblatt, *Surf. Sci.*, 1980, **97**, 346–362.
- T. Root, L. Schmidt and G. B. Fisher, *Surf. Sci.*, 1983, **134**, 30–45.
- P. Ho and J. White, *Surf. Sci.*, 1984, **137**, 103–116.
- L. A. DeLouise and N. Winograd, *Surf. Sci.*, 1985, **159**, 199–213.
- T. Root, G. B. Fisher and L. Schmidt, *J. Chem. Phys.*, 1986, **85**, 4679–4686.
- T. Root, G. B. Fisher and L. Schmidt, *J. Chem. Phys.*, 1986, **85**, 4687–4695.
- M. Bowker, Q. Guo and R. Joyner, *Surf. Sci.*, 1991, **257**, 33–40.
- M. Van Tol and B. Nieuwenhuys, *Appl. Surf. Sci.*, 1993, **67**, 188–197.
- H. Borg, J. J. Reijerse, R. Van Santen and J. Niemantsverdriet, *J. Chem. Phys.*, 1994, **101**, 10052–10063.
- Y. J. Kim, S. Thevuthasan, G. S. Herman, C. H. Peden, S. A. Chambers, D. N. Belton and H. Permana, *Surf. Sci.*, 1996, **359**, 269–279.
- D. Loffreda, D. Simon and P. Sautet, *J. Chem. Phys.*, 1998, **108**, 6447–6457.
- A. Beniya, T. Koitaya, H. Kondoh, K. Mukai, S. Yoshimoto and J. Yoshinobu, *J. Chem. Phys.*, 2009, **131**, 084704.
- M. Hopstaken and J. Niemantsverdriet, *J. Phys. Chem. B*, 2000, **104**, 3058–3066.
- K. Sato, T. Yoshinari, Y. Kintaichi, M. Haneda and H. Hamada, *Appl. Catal., B*, 2003, **44**, 67–78.
- A. Arab, M. Nahali and F. Gopal, *J. Alloys Compd.*, 2017, **695**, 1924–1929.
- A. Wang, J. Li and T. Zhang, *Nat. Rev. Chem.*, 2018, **2**, 65–81.
- J.-C. Liu, Y. Tang, Y.-G. Wang, T. Zhang and J. Li, *Nat. Sci. Rev.*, 2018, **5**, 638–641.
- X. Li, S. Mitchell, Y. Fang, J. Li, J. Perez-Ramirez and J. Lu, *Nat. Rev. Chem.*, 2023, **7**, 754–767.
- M. L. Anderson, M. S. Ford, P. J. Derrick, T. Drewello, D. P. Woodruff and S. R. Mackenzie, *J. Phys. Chem. A*, 2006, **110**, 10992–11000.
- P. Ghosh, R. Pushpa, S. de Gironcoli and S. Narasimhan, *J. Chem. Phys.*, 2008, **128**, 194708.
- M. Torres, F. Aguilera-Granja, L. Balbás and A. Vega, *J. Phys. Chem. A*, 2011, **115**, 8350–8360.
- H. Xie, M. Ren, Q. Lei and W. Fang, *J. Phys. Chem. A*, 2011, **115**, 14203–14208.
- S. Romo-Ávila and R. Guirado-López, *J. Phys. Chem. A*, 2012, **116**, 1059–1068.
- Y. Tawaraya, S. Kudoh, K. Miyajima and F. Mafune, *J. Phys. Chem. A*, 2015, **119**, 8461–8468.
- H.-Q. Yang, H.-Q. Fu, B.-F. Su, B. Xiang, Q.-Q. Xu and C.-W. Hu, *J. Phys. Chem. A*, 2015, **119**, 11548–11564.
- F. Mafuné, M. Takenouchi, K. Miyajima and S. Kudoh, *J. Phys. Chem. A*, 2016, **120**, 356–363.
- T. Nagata, K. Kawada, X. Chen, M. Yamaguchi, K. Miyajima and F. Mafuné, *Phys. Chem. Chem. Phys.*, 2021, **23**, 26721–26728.
- Y.-X. Zhao, X.-G. Zhao, Y. Yang, M. Ruan and S.-G. He, *J. Chem. Phys.*, 2021, **154**, 180901.
- J.-J. Chen, S.-D. Wang, Z.-Y. Li, X.-N. Li and S.-G. He, *J. Am. Chem. Soc.*, 2023, **145**, 18658–18667.
- E. German, G.-L. Hou, J. Vanbuel, J. M. Bakker, J. A. Alonso, E. Janssens and M. J. López, *Carbon*, 2022, **197**, 535–543.
- G.-L. Hou, T. Yang, M. Li, J. Vanbuel, O. V. Lushchikova, P. Ferrari, J. M. Bakker and E. Janssens, *Angew. Chem., Int. Ed.*, 2021, **60**, 27095–27101.
- M. Li, T. Yang, J. M. Bakker, E. Janssens and G.-L. Hou, *Cell Rep. Phys. Sci.*, 2022, **3**, 100910.
- G.-L. Hou and E. Janssens, *Fundam. Res.*, 2023, DOI: [10.1016/j.fmre.2023.10.011](https://doi.org/10.1016/j.fmre.2023.10.011).
- J. Zheng, L. Huang, C. H. Cui, Z. C. Chen, X. F. Liu, X. Duan, X. Y. Cao, T. Z. Yang, H. Zhu, K. Shi, P. Du, S. W. Ying, C. F. Zhu, Y. G. Yao, G. C. Guo, Y. Yuan, S. Y. Xie and L. S. Zheng, *Science*, 2022, **376**, 288–292.
- M. J. Frisch, G. W. Trucks, H. B. Schlegel, G. E. Scuseria, M. A. Robb, J. R. Cheeseman, G. Scalmani, V. Barone, B. Mennucci, G. A. Petersson, H. Nakatsuji, X. Li, H. P. Hratchian, A. F. Izmaylov, J. Bloino, G. Zheng, J. L. Sonnenberg, M. Hada, M. Ehara, K. Toyota, R. Fukuda, J. Hasegawa, M. Ishida, T. Nakajima, Y. Honda, O. Kitao, H. Nakai, T. Vreven, J. A. Montgomery Jr., J. E. Peralta, F. Ogliaro, M. Bearpark, J. J. Heyd, E. Brothers, K. N. Kudin, V. N. Staroverov, T. Keith, R. Kobayashi, J. Normand, K. Raghavachari, A. Rendell, J. C. Burant, S. S. Iyengar, J. Tomasi, M. Cossi, N. Rega, J. M. Millam, M. Klene, J. E. Knox, J. B. Cross, V. Bakken, C. Adamo, J. Jaramillo, R. Gomperts, R. E. Stratmann, O. Yazyev, A. J. Austin, R. Cammi, C. Pomelli, J. W. Ochterski, R. L. Martin, K. Morokuma, V. G. Zakrzewski, G. A. Voth, P. Salvador, J. J. Dannenberg, S. Dapprich, A. D. Daniels, O. Farkas, J. B. Foresman, J. V. Ortiz, J. Cioslowski and D. J. Fox, *Gaussian 09, Revision E.01*, Gaussian, Inc, Wallingford CT, 2013.
- A. D. Becke, *Phys. Rev. A: At., Mol., Opt. Phys.*, 1988, **38**, 3098–3100.
- J. P. Perdew, in *Electronic Structure of Solids '91*, ed. P. Ziesche and H. Eschrig, Akademie Verlag, Berlin, 1991, p. 11.

- 43 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.
- 44 A. D. Becke, *J. Chem. Phys.*, 1993, **98**, 5648–5652.
- 45 C. Lee, W. Yang and R. G. Parr, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1988, **37**, 785–789.
- 46 D. Andrae, U. Haeussermann, M. Dolg, H. Stoll and H. Preuss, *Theor. Chim. Acta*, 1990, **77**, 123–141.
- 47 J. Xu, J. M. Bakker, O. V. Lushchikova, P. Lievens, E. Janssens and G.-L. Hou, *J. Am. Chem. Soc.*, 2023, **145**, 22243–22251.
- 48 J. Xu, A. Li, X. Li and G.-L. Hou, *Mon. Not. R. Astron. Soc.*, 2023, **525**, 3061–3074.
- 49 K. Fukui, *Acc. Chem. Res.*, 1981, **14**, 363–368.
- 50 A. E. Reed, R. B. Weinstock and F. Weinhold, *J. Chem. Phys.*, 1985, **83**, 735–746.