



Cite this: *Nanoscale*, 2023, **15**, 1824

# Dielectric behaviour of plasma hydrogenated TiO<sub>2</sub>/cyanoethylated cellulose nanocomposites†

Nadeesh M. Adassooriya,<sup>a</sup> Dilek Ozgit,<sup>a</sup> Sai G. Shivareddy,<sup>a</sup> Pritesh Hiralal,<sup>a</sup> Damayanthi Dahanayake,<sup>b</sup> Rachel A. Oliver<sup>c</sup> and Gehan A. J. Amaratunga<sup>\*a</sup>

The interface between the polymer and nanoparticle has a vital role in determining the overall dielectric properties of a dielectric polymer nanocomposite. In this study, a novel dielectric nanocomposite containing a high permittivity polymer, cyanoethylated cellulose (CRS) and TiO<sub>2</sub> nanoparticles surface modified by hydrogen plasma treatments was successfully prepared with different weight percentages (10%, 20% and 30%) of hydrogenated TiO<sub>2</sub>. Internal structure of H plasma treated TiO<sub>2</sub> nanoparticles (H-TiO<sub>2</sub>) and the intermolecular interactions and morphology within the polymer nanocomposites were analysed. H-TiO<sub>2</sub>/CRS thin films on SiO<sub>2</sub>/Si wafers were used to form metal–insulator–metal (MIM) type capacitors. Capacitances and loss factors in the frequency range of 1 kHz to 1 MHz were measured. At 1 kHz H-TiO<sub>2</sub>/CRS nanocomposites exhibited ultra-high dielectric constants of 80, 118 and 131 for nanocomposites with 10%, 20% and 30% weight of hydrogenated TiO<sub>2</sub> respectively, significantly higher than values of pure CRS (21) and TiO<sub>2</sub> (41). Furthermore, all three H-TiO<sub>2</sub>/CRS nanocomposites show a loss factor <0.3 at 1 kHz and low leakage current densities (10<sup>−6</sup> A cm<sup>−2</sup>–10<sup>−7</sup> A cm<sup>−2</sup>). Leakage was studied using conductive atomic force microscopy (C-AFM) and it was observed that the leakage is associated with H-TiO<sub>2</sub> nanoparticles embedded in the CRS polymer matrix. Although, modified interface slightly reduces energy densities compared to pristine TiO<sub>2</sub>/CRS system, the capacitance values for H-TiO<sub>2</sub>/CRS in the voltage range of −2 V to 2 V are very stable. Whilst H-TiO<sub>2</sub>/CRS possesses ultra-high dielectric constants (>100), this study reveals that the polymer nanoparticle interface has a potential influence on dielectric behaviour of the composite.

Received 26th August 2022,  
Accepted 15th December 2022

DOI: 10.1039/d2nr04680f

[rsc.li/nanoscale](http://rsc.li/nanoscale)

## Introduction

Capacitors are used ubiquitously in all electronic circuits and systems for transient energy storage and ballasting. Energy density achievable in a capacitor will determine its physical size in an electronic system.<sup>1</sup> Very often the capacitor size is a limiting factor in minimising the overall size and weight of an electronic system. This is a pressing issue especially in portable and mobile electronic systems in applications ranging from wearable sensors to electric vehicles. At present the higher energy rated are bulky electrolytic capacitors. One

promising route to replacing electrolytic capacitors is to have thin film dielectric capacitors with higher energy density.<sup>2</sup> In turn, the energy densities of dielectric capacitors are limited by the relative permittivity of the dielectric material. As a result, within the past decade there has been significant research effort directed at developing higher permittivity dielectric materials for capacitors.<sup>3</sup>

One route being explored to achieve high effective permittivity is to form a composite of two (or more in principle) dielectrics. However, the challenge is to achieve an increase in the effective permittivity of the dielectric without increasing its effective thickness, which would reduce capacitance, beyond that required for sustaining the electric field without breakdown at the specified operating voltage. One possible way of achieving this is to introduce one of the materials in nanoparticle form within the other *i.e.* a nanocomposite.<sup>4</sup> This has the advantage of maximising surface (interface) area to volume ratio of the material included in nanoparticle form. In recent years, it has been shown that with the introduction of nano-sized fillers into polymer matrices significantly higher dielectric constants compared the dielectric constant of the filler

<sup>a</sup>Electrical Engineering Division, Department of Engineering, University of Cambridge, 9 JJ Thomson Avenue, Cambridge CB3 0FA, UK.

E-mail: [gaja1@cam.ac.uk](mailto:gaja1@cam.ac.uk); Fax: +44 (0)1223748348; Tel: +44 (0)1223 748325

<sup>b</sup>Sri Lanka Institute of Nanotechnology (SLINTEC), Mahenawatta, Pitipana, Homagama, CO 10206, Sri Lanka

<sup>c</sup>Department of Materials Science and Metallurgy, University of Cambridge, 27 Charles Babbage Road, Cambridge, CB3 0FS, UK

†Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2nr04680f>



could be achieved. This increase in effective dielectric constant has been ascribed to polarisation phenomena at the nanoparticle–polymer interfaces.<sup>5</sup>

It is in this vein that nanosized fillers have been introduced into dielectric polymer matrix to form dielectric polymer nanocomposites. Enhanced dielectric properties with low leakage currents while preserving the facile processability, flexibility and lightness of the polymer matrix have been reported.<sup>6–8</sup> TiO<sub>2</sub> is a versatile material used in a range of applications including nanodielectrics where composites of nanoscale TiO<sub>2</sub> with different polymers form the dielectric.<sup>9–18</sup> In 1988, Bandyopadhyay *et al.* reported the first dielectric nanocomposite based on TiO<sub>2</sub> nanoparticle and polystyrene.<sup>9</sup> Afterwards, in 1994 Lewis<sup>10</sup> reported a landmark theoretical study on dielectric nanocomposites the significance which was recognised after publication of the experimental work on TiO<sub>2</sub>–epoxy resin dielectric nanocomposite ( $k = 8.5$  at 1 kHz for 500–750  $\mu\text{m}$  thick films) published by Nelson *et al.* in 2002.<sup>11</sup> In 2004, Cheng *et al.* reported a cross linked poly-4-vinylphenol–TiO<sub>2</sub> dielectric nanocomposite with dielectric constant of 7.5 at 50 kHz. Maliakal *et al.* achieved over 3 times enhancement of dielectric constant compared to that of bulk polystyrene for a 1.25  $\mu\text{m}$  thick core shell TiO<sub>2</sub>–polystyrene nanocomposite films at 1 kHz.<sup>12</sup> Nanocomposites of polypyrrole/TiO<sub>2</sub> ( $k = 140$  at 1 kHz for 0.5 mm thick films),<sup>13</sup> PMMA/TiO<sub>2</sub> ( $k = 25$  at 1 kHz for 5 mm thick films),<sup>14</sup> poly(vinylidene fluoride-*ter*-trifluoroethylene)-TiO<sub>2</sub> ( $k = 12$  at 1 kHz for 25–50  $\mu\text{m}$  thick films)<sup>15</sup> and poly(vinylidene fluoride-*ter*-trifluoroethylene-*ter*-chlorotrifluoroethylene)-TiO<sub>2</sub> ( $k = 42$  at 1 kHz for 25–50  $\mu\text{m}$  thick films),<sup>16</sup> PEOX–PVP–TiO<sub>2</sub> nanocomposite ( $k = 18.56$  at 1 kHz 0.40 mm thick films)<sup>17</sup> have been reported subsequently in the literature. In our previous work we explored the use of TiO<sub>2</sub> nanoparticles within a high dielectric polymer called cyanoethylated cellulose (CRS) and reported effective relative permittivities in excess of 200 ( $k = 207$  at 1 kHz, 25 nm TiO<sub>2</sub> particles, 120 nm thin films); 10 times higher than that of the pristine CRS polymer.<sup>18</sup> CRS is a cellulose derivative with very high dielectric constant ( $k = 21$  at 1 kHz) compared to other dielectric polymers, but has received comparatively less attention in the literature. Dipoles of CO and CN present in CRS are responsible for dielectric behaviour and due to the polar nature of the polymer matrix, it also shows a strong affinity for inorganic oxides.<sup>19</sup> In addition, dielectric behaviour of CRS/BaTiO<sub>3</sub> ( $k = 133$  at 1 kHz, 2-micron BaTiO<sub>3</sub> particles and film thickness 100–350  $\mu\text{m}$ )<sup>20</sup> and MMT/CRS ( $k = 71$  at 1 kHz, 180 nm thin films)<sup>21</sup> have been reported in the literature. Here we further explore the TiO<sub>2</sub> nanoparticle system by subjecting the surface to a plasma treatment. The aim is to see whether the effective interface charge density can be enhanced by introducing additional surface states through mild plasma etching.

In the hydrogenation process TiO<sub>2</sub> nanoparticles are treated in hydrogen containing environment or hydrogen plasma at defined temperatures for certain period of time. During this process the surface of the TiO<sub>2</sub> nanoparticles completely change as it forms a highly disordered surface layer containing

large number of oxygen vacancies, Ti<sup>3+</sup> though self-doping, surface hydroxyl groups and T–H bonds. Hydrogenated TiO<sub>2</sub> or black TiO<sub>2</sub> is now one of the most attractive materials in the areas of photocatalysis, electrochemical solar cells, supercapacitors and batteries.<sup>22–25</sup>

## Experimental

### Materials

TiO<sub>2</sub> anatase nanoparticles and acetone were purchased from Sigma Aldrich, USA and CRS polymer were purchased from Shin-Etsu Chemical Co. Ltd Japan. All chemicals were used without further purification.

### Hydrogenation of TiO<sub>2</sub> NPs using hydrogen plasma

TiO<sub>2</sub> nanoparticles (100 mg) were dispersed in ethanol (50 ml) with the aid of ultrasonication for 10 min. Then solution was drop cast on a Si wafer. Drop casting was repeated several times to obtain a thick TiO<sub>2</sub> layer on the Si wafer. Prepared TiO<sub>2</sub> films were exposed to an H plasma for 2–10 min. The H<sub>2</sub> plasma treatment was performed at 500 °C and 3.6 mbar pressure. Plasma power was 50 W and H<sub>2</sub> flow rate was 50 sccm.

### Preparation of films of H plasma treated TiO<sub>2</sub> nanocomposite

CRS polymer was dissolved in acetone to prepare a polymer solution and different volumes of polymer solution were mixed with H-TiO<sub>2</sub> nanoparticles and stirred for 24 hours to obtain H-TiO<sub>2</sub>/CRS dispersions with different H-TiO<sub>2</sub> weight percentages; 10% (3.45 vol%), 20% (6.65 vol%) and 30% (9.65 vol%) respectively. Spin coating of H-TiO<sub>2</sub>/CRS dispersions at 2500 rpm for 20 s was used to deposit polymer nanocomposite films on clean n-type Si wafer (with a 200 nm SiO<sub>2</sub> layer). This was followed by thermal annealing at 150 °C for 3 hours.

### Fabrication of metal–insulator–metal (MIM) type capacitors

H-TiO<sub>2</sub>/CRS nanocomposite films on SiO<sub>2</sub>/Si wafers were used to form metal–insulator–metal (MIM) type capacitors (100 nm Al layers deposited by thermal evaporation were used as metal top and bottom electrodes). Capacitance measurements of the nanocomposites over a range of frequencies from 1 kHz to 1 MHz, capacitance–voltage measurements and current–voltage measurements were performed on a Microtech cascade probe station.

### Characterisation H-TiO<sub>2</sub>/CRS nanocomposite

PXRD data of the dielectric films were collected on a Phillips PW3710 diffractometer with nickel-filtered CuK $\alpha$  radiation (1.5406 Å) using a scanning RTMS X'Celerator detector. The morphology and film thickness were analysed by Scanning Electron Microscopy (SEM) using a HITACHI SS5500 microscope. Conductive atomic force microscopy (C-AFM) was carried out on a Veeco Dimension 3100 atomic force microscope (AFM) using a commercially-available extended tunneling atomic force microscopy (extended-TUNA)



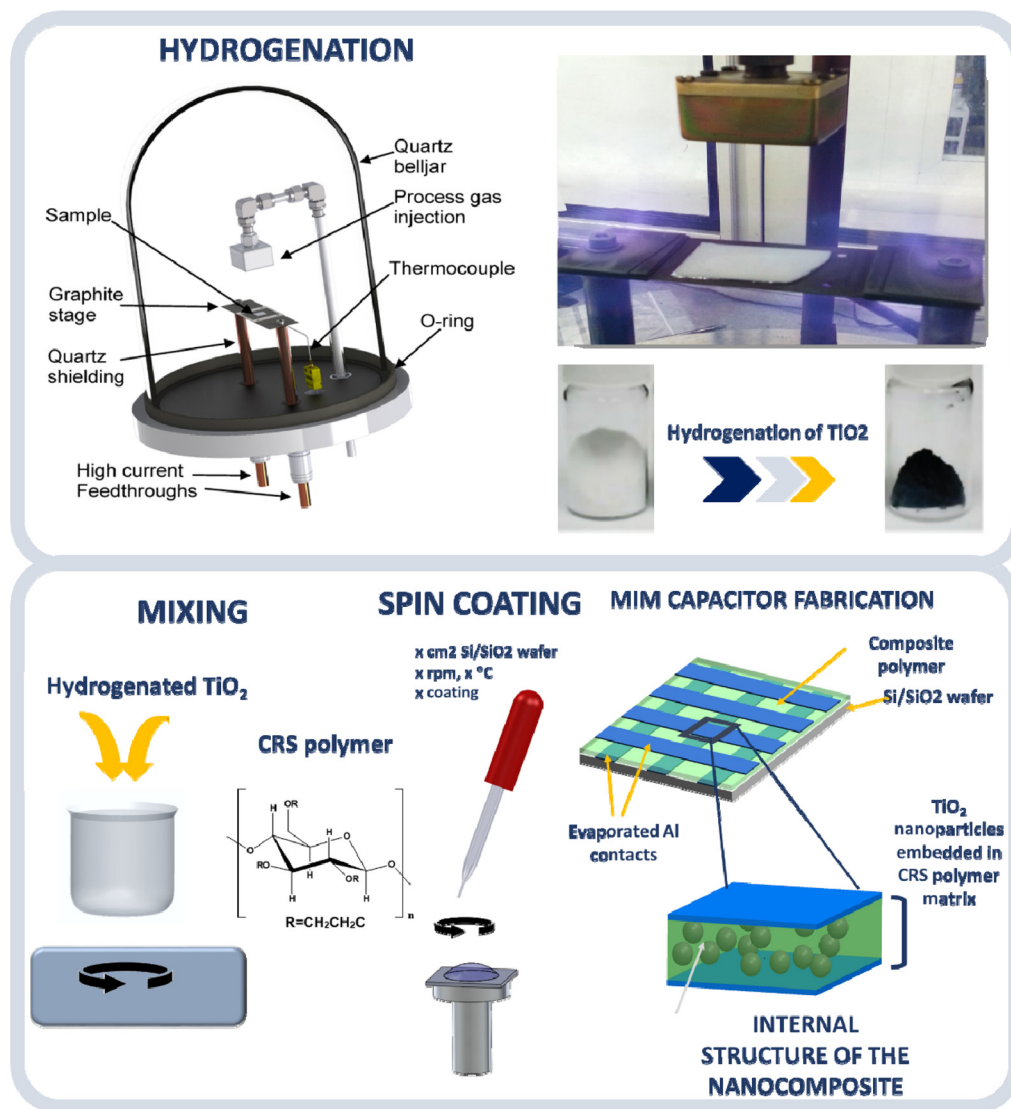


Fig. 1 Stepwise preparation of MIM capacitors with H plasma treated  $\text{TiO}_2$ -CRS nanocomposite thin films.

module. Platinum-iridium coated probes (from Veeco, model: SCM-PIC) were used. X-ray photoelectron spectroscopy (XPS) was carried out using a ESCALAB 250 Xi equipped with a monochromatic Al  $K\alpha$  X-ray source in an ultrahigh vacuum. Ultra-violet photoemission spectroscopy (UPS) was also carried out using a ESCALAB 250 Xi with a UV excitation source of He-I emission at 21.21 eV in an ultrahigh vacuum. Fourier transform infra-red spectroscopy was performed using a Bruker Vertex80 in the range from 600 to 4000  $\text{cm}^{-1}$  using the attenuated total reflectance technique. Transmission electron microscopy characterisation was performed at room temperature on a Philips CM30 instrument operating at 300 kV. TEM images, electron diffraction patterns and EELs spectra were recorded. NMR Spectrum for hydrogenated  $\text{TiO}_2$  was recorded on a Bruker Advance 400 spectrometer tuned to 500 MHz for  $^1\text{H}$  NMR. A 4 mm probe was used spinning at 6 kHz. 1000 transients were collected using an 8 s recycle delay and a rf field of

60 kHz. Elemental analysis (hydrogen) of hydrogenated  $\text{TiO}_2$  was performed using a CE-440 Exeter Analytical, Inc. elemental analyser. Schematic representation of fabrication of MIM capacitor starting from pristine  $\text{TiO}_2$  and CRS polymer is given in the Fig. 1.

## Results and discussion

### Hydrogen plasma treated $\text{TiO}_2$ nanoparticles

**PXRD, FTIR and UV/Vis analysis of hydrogen plasma treated  $\text{TiO}_2$  nanoparticles.** The PXRD patterns of the pristine  $\text{TiO}_2$  and H plasma treated  $\text{TiO}_2$  nanoparticles (10 min H plasma exposure at 500  $^\circ\text{C}$ ), are shown in Fig. 2(a). There is no obvious difference between the X-ray diffraction patterns of pristine and hydrogenated  $\text{TiO}_2$  indicating that there is no phase transformation during the H plasma treatment.<sup>26</sup>



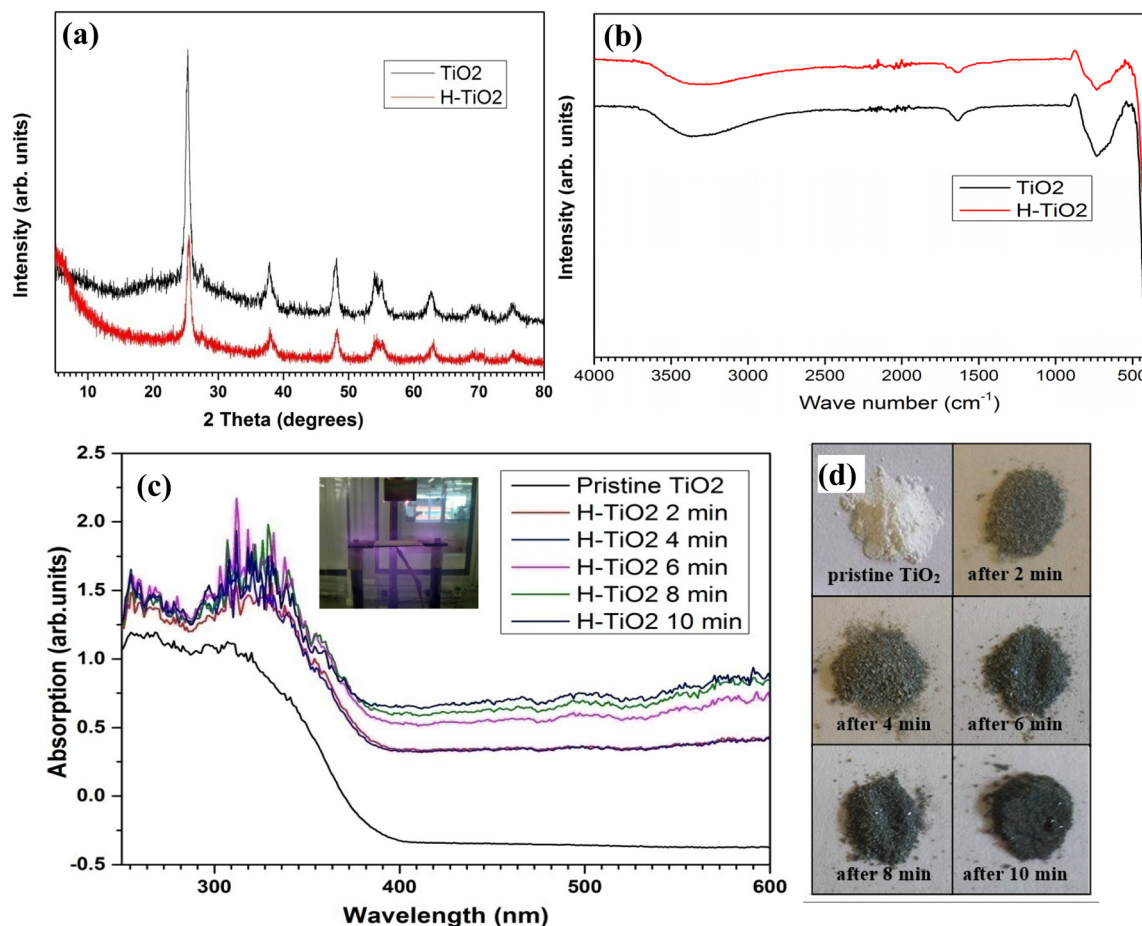


Fig. 2 PXRD patterns of (a) FTIR spectra (b) of  $\text{TiO}_2$  and H plasma treated  $\text{TiO}_2$  and (c) UV-visible spectra and (d) corresponding photographs of H plasma treated for different exposure time.

FTIR spectra for pristine  $\text{TiO}_2$  and H- $\text{TiO}_2$  are shown in Fig. 2(b). Both pristine  $\text{TiO}_2$  and H- $\text{TiO}_2$  show same IR activity; absorption bands at  $3350\text{ cm}^{-1}$ ,  $1630\text{ cm}^{-1}$  and  $734\text{ cm}^{-1}$  are due to O–H stretching, O–H bending of surface adsorbed water and Ti–O stretching mode of  $\text{TiO}_2$  respectively.

Fig. 2(c) shows the UV-Visible absorption spectra for pristine  $\text{TiO}_2$  and H- $\text{TiO}_2$  with different reaction times. It was observed that a significant change in the absorption intensity in the UV region and the absorption in the visible light region gradually increased with extended hydrogenation time. This can be attributed to the colour change in the material, where the white colour of the pristine  $\text{TiO}_2$  turns into black. The optical absorption characteristics suggest that H plasma treatment introduces surface defect states within the band gap of the  $\text{TiO}_2$ .<sup>26–28</sup> Fully black H plasma treated  $\text{TiO}_2$  sample for 10 min at  $500^\circ\text{C}$  was used for all the other characterisations and nanocomposite formation from here on.

#### Electron microscopy on hydrogen plasma treated $\text{TiO}_2$ nanoparticles

SEM and STEM images for pristine  $\text{TiO}_2$  and H- $\text{TiO}_2$  are shown in Fig. 3. Pristine  $\text{TiO}_2$  shows spherical morphology with

25 nm average particle size. After hydrogenation, morphology and particle size remain unchanged. However, it was observed H- $\text{TiO}_2$  particles are more aggregated compared to pristine  $\text{TiO}_2$  NPs.

HR TEM images and electron diffraction patterns for pristine  $\text{TiO}_2$  and H- $\text{TiO}_2$  are shown in Fig. 4.

#### Electron energy loss (EEL), solid state proton NMR, XPS analysis and band gap calculation of hydrogen plasma treated $\text{TiO}_2$ nanoparticles

As seen from the well resolved lattice features in Fig. 4(a) and (b), both pristine and H plasma treated  $\text{TiO}_2$  are highly crystalline and significant differences are not observed in the HR TEM images. However, fast Fourier transform analysis images (FFT) of pristine  $\text{TiO}_2$  contains more and brighter diffraction spots compared to H- $\text{TiO}_2$ . This is indicative of some distortion in the  $\text{TiO}_2$  atomic lattice structure after the hydrogenation process and is consistent with optical absorption indication the introduction defect states within the band gap. Furthermore, in Fig. 5(a) the Electron Energy Loss (EEL) spectra for pristine  $\text{TiO}_2$  and H- $\text{TiO}_2$ , shows that the peak at  $464.8\text{ eV}$  for pristine  $\text{TiO}_2$  has shifted to  $465.8\text{ eV}$  after H





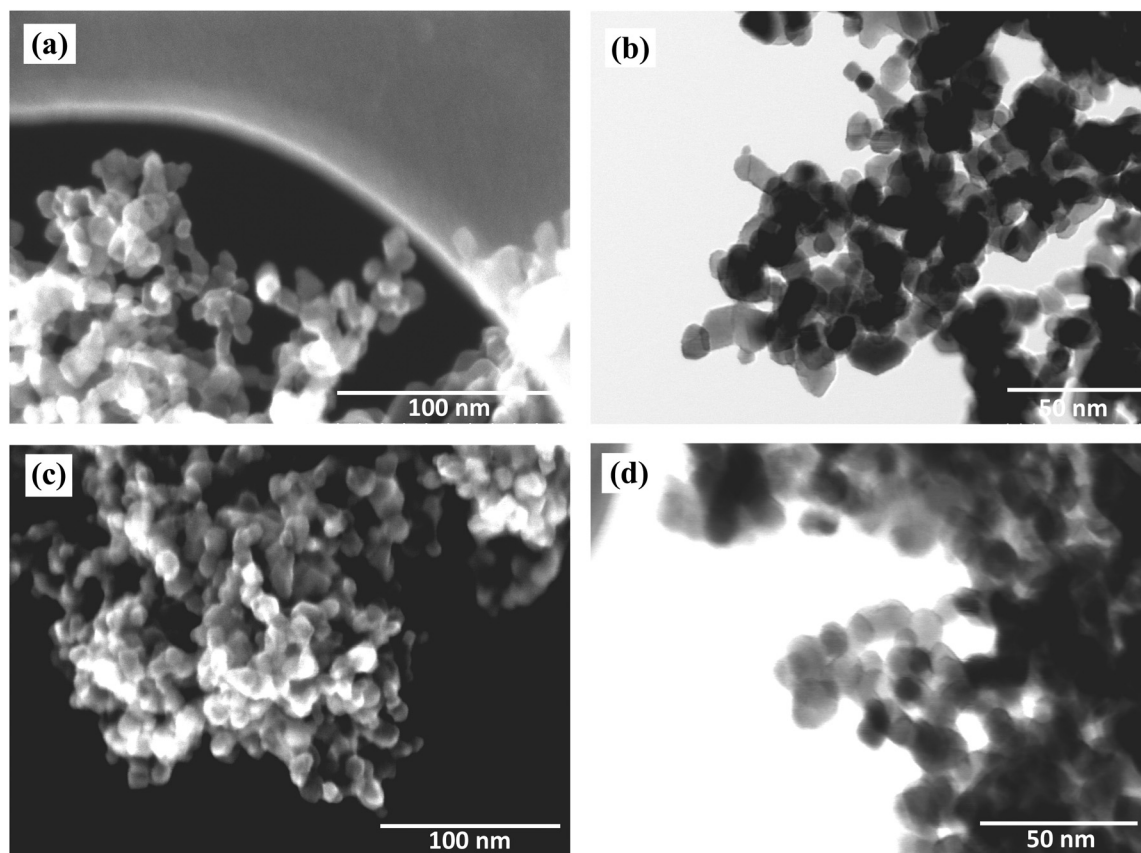


Fig. 3 SEM (a) and STEM (b) images of  $\text{TiO}_2$  nanoparticles and SEM (c) and STEM (d) images of H plasma treated  $\text{TiO}_2$  nanoparticles.

plasma treatment. The chemical shift can be due to the change in charge transfer from Ti to O in H plasma treated  $\text{TiO}_2$ . This is further evidence of the chemical changes in the  $\text{TiO}_2$  surface during hydrogenation *via* H plasma treatment. The EELS spectrum of pristine  $\text{TiO}_2$  is in good agreement with previously reported data in the literature. Ti  $L_{3,2}$  edge in  $\text{TiO}_2$  shows two spectral lines split into two maxima due to crystal field splitting where octahedral coordination of Ti atom with O splits into degenerate 3d states.

H-NMR spectra of pristine  $\text{TiO}_2$  and H- $\text{TiO}_2$  nanoparticles show broad peaks at chemical shifts of 9.3 ppm and 7.6 ppm respectively. However, H- $\text{TiO}_2$  nanoparticles shows two small additional peaks at 4.0 ppm and 2.4 ppm which could be ascribed the presence of weakly bound hydrogen atoms as a result of the H plasma treatment. The multiplicity of the NMR peaks can be used to identify the number of H environments within the sample. The peaks at 4.0 ppm and 2.4 ppm can be attributed to bridging and terminal titanol groups.<sup>29</sup>

XPS analysis of Ti 2p region reveals a slight shift of binding energies as shown in Fig. 5(c). The Ti 2p XPS spectra shows two main peaks at 458.4 eV and 463.9 eV due to the spin-orbit pairs of  $2p^{3/2}$  and  $2p^{1/2}$ . In addition, a satellite peak at 471 eV was observed.<sup>31</sup> A similar trend was observed for the Ti 2p in H- $\text{TiO}_2$  ( $2p^{3/2}$  peak at 458.6 eV,  $2p^{1/2}$  peak at 464.3 eV and satellite peak at 472 eV). These slight changes in the binding ener-

gies can be attributed to the oxygen vacancy formation in the  $\text{TiO}_2$  surface. A notable change in the binding energies of O 1s was not observed in agreement with previous studies. HOMO and LUMO energy levels of H plasma treated  $\text{TiO}_2$  NPs were extracted using UV/Vis Fig. 5(d) and UPS data (Fig. S1†). It was observed that band gap of pristine  $\text{TiO}_2$  NPs (3.20 eV) has reduced to 3.1 eV following the hydrogenation process which is in agreement with the previous studies.<sup>26</sup> HOMO level of energy of pristine  $\text{TiO}_2$  measured in our previous work was -7.5 eV. H- $\text{TiO}_2$  gives a HOMO value of 5.90 eV during the hydrogenation process. This is a very significant shift of 1.6 eV. UPS probes the first 2–3 nm of the surface of the nanoparticles. The NMR shows that the surface of the H- $\text{TiO}_2$  has titanol groups. The surface modification through the titanol groups may contribute to the shift in the HOMO energy measured. In addition to above characterisation techniques, elemental analysis for hydrogen was performed on hydrogenated  $\text{TiO}_2$  samples and it shows that 0.2% of average weight percentage of hydrogen is present. It suggests that  $\text{TiO}_2$ :H molecular ratio is roughly 5 : 1. Pristine  $\text{TiO}_2$  did not give any significant reading.

#### H- $\text{TiO}_2$ /CRS nanocomposites and MIM capacitors

**PXRD, SEM and XPS analysis of H- $\text{TiO}_2$ /CRS nanocomposites.** The PXRD traces of H- $\text{TiO}_2$ /CRS nanocomposites,



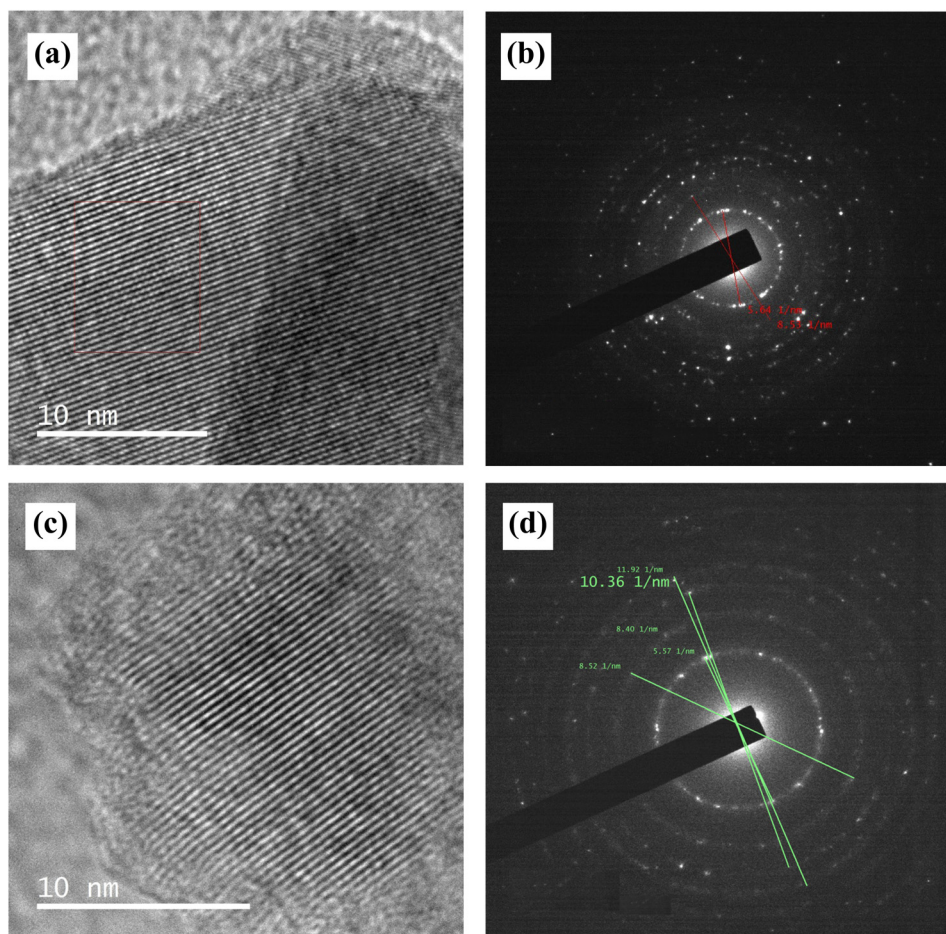


Fig. 4 HR TEM (a) and FFT (b) images of  $\text{TiO}_2$  nanoparticles and HR TEM (c) and FFT (d) images of H plasma treated  $\text{TiO}_2$  nanoparticles.

H- $\text{TiO}_2$  and CRS polymer are given in Fig. 6(a). The peak positions of the H- $\text{TiO}_2$  sample are consistent with the anatase phase of  $\text{TiO}_2$  and there is no change in the crystal phase of H- $\text{TiO}_2$  when it is incorporated into a CRS polymer matrix. In addition, the amorphous nature is observed by the broad peaks at around  $10^\circ$  and  $25^\circ 2\theta$  for both bare polymer and for the CRS matrix of the composite. Fig. 6(b) shows a cross section of a H- $\text{TiO}_2$ /CRS thin film on the Al bottom contact on the  $\text{SiO}_2$  200 nm/Si wafer.

X-ray photoelectron spectroscopy of the N 1s peak from the bare CRS polymer and H- $\text{TiO}_2$ /CRS and Ti 2p peak from bare  $\text{TiO}_2$  and H- $\text{TiO}_2$ /CRS are shown in Fig. 6(c). The N 1s spectra for the CRS polymer showed two major peaks with binding energies of 397.4 eV and 397.9 eV whereas, N 1s spectra for the H- $\text{TiO}_2$ /CRS resolved into three peaks at 400.3 eV, 401.5 eV and 402.5 eV. The shifting of the binding energy of N 1s in the CN group of the polymer confirms the interaction of the CRS polymer with H- $\text{TiO}_2$  nanoparticles. In Fig. 6(d) the Ti 2p XPS spectra for H- $\text{TiO}_2$  shows two main peaks at 457.2 eV and 462.8 eV due to the spin-orbit pairs of  $2p^{3/2}$  and  $2p^{1/2}$ . In addition, a satellite peak at 470.4 eV was observed. For H- $\text{TiO}_2$ /CRS; the Ti  $2p^{3/2}$  and  $2p^{1/2}$  peaks are shifted to 461.3 eV and 466.8 eV respectively. However, satellite peak was not observed.

A notable change in the binding energies of C 1s and O 1s were not observed. Furthermore, N 1s spectral line of CRS-H- $\text{TiO}_2$  has shifted to higher values compared to CRS- $\text{TiO}_2$  nanocomposite. This can be ascribed as to the changes that arise in the electronic structure of H- $\text{TiO}_2$  during hydrogenation which facilitate the bonding interactions of H- $\text{TiO}_2$  with the CRS polymer matrix. The XPS data suggest that the interaction of the CRS with H- $\text{TiO}_2$  occurs *via* interactions of Ti with N to TiN type complexes.<sup>30</sup>

#### Electrical properties of H- $\text{TiO}_2$ /CRS nanocomposites MIM capacitors

The capacitances of the H- $\text{TiO}_2$ /CRS nanocomposite films and bare CRS polymer were measured in the frequency range from 1 kHz to 1 MHz and are shown together with their respective dielectric constants in Fig. 7(a) and (b).

The capacitance values for the bare polymer and 10% weight CRS-H- $\text{TiO}_2$  composite remain constant up to 500 kHz and then gradually decreases with increasing frequency. For 20% and 30% weight H- $\text{TiO}_2$ /CRS composite, capacitance values sharply decrease after 10 kHz with increasing frequency. This behaviour is due to the relaxation process in H- $\text{TiO}_2$ /CRS interface.<sup>31</sup>



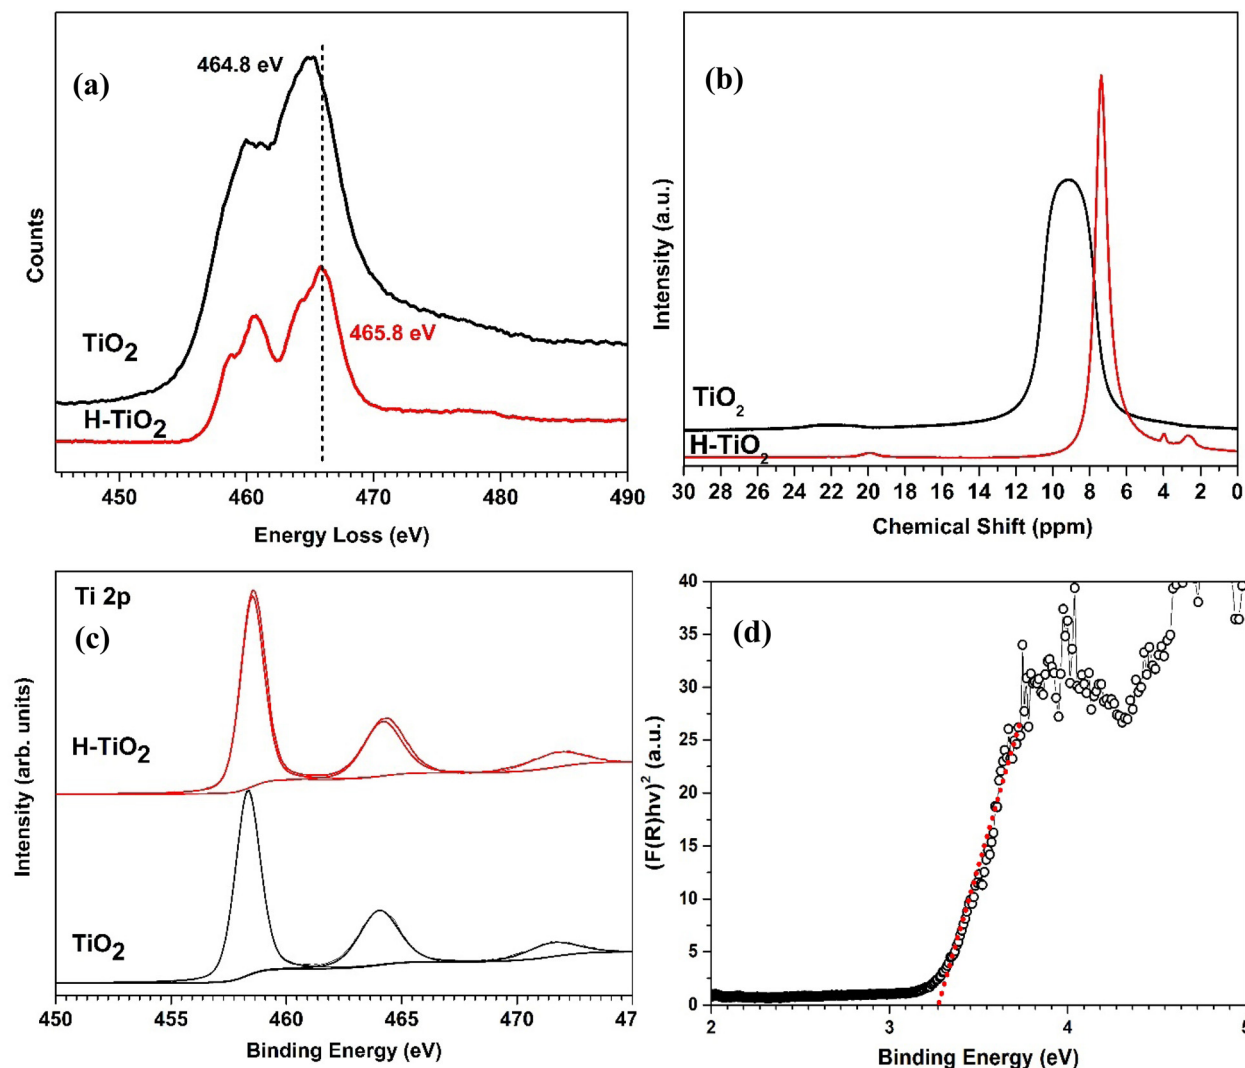


Fig. 5 (a) EEL spectra (b)  $^1\text{H}$ -NMR spectra (c) XPS Ti 2p spectra and (d) UV absorption spectra arranged according to the Kubelka–Munk function for  $\text{H-TiO}_2$  NPs.

However, capacitance values for all  $\text{TiO}_2/\text{CRS}$  nanocomposites reported in our previous work are stable up to 500 Hz compared to  $\text{H-TiO}_2/\text{CRS}$  nanocomposites. This suggests that the addition of H plasma treated  $\text{TiO}_2$  initiates the relaxation process at lower frequencies compared to pristine  $\text{TiO}_2$ , in the CRS matrix. Which is consistent with the H plasma treatment creating surface defect states deep in the band gap which take longer to fill/empty. Dielectric constants for all three composites were calculated using the average film thickness measured by AFM (Fig. S2†). At 1 kHz CRS- $\text{H-TiO}_2$  nanocomposites exhibited high dielectric constants of 80, 118 and 131 with 10%, 20% and 30% weight of  $\text{H-TiO}_2$  respectively which is significantly higher than of pure CRS. Fig. 7(c) shows capacitance–voltage measurements for all three nanocomposite films and bare CRS polymer and it was observed that capacitance values for all three nanocomposites and bare CRS polymer in the voltage range of  $-2$  V to  $2$  V are very stable. The leakage current densities are relatively low, in the range of


$10^{-6}$  A  $\text{cm}^{-2}$ – $10^{-8}$  A  $\text{cm}^{-2}$ . However, as seen in  $\text{TiO}_2/\text{CRS}$  nanocomposites,<sup>5</sup> the  $\text{H-TiO}_2/\text{CRS}$  current voltage characteristics also possess a distinct asymmetry and a shift in the zero current up to  $1$  V is seen for composites with different  $\text{TiO}_2$  loading. This shift in the minimum current from  $0$  V could be due to the charging of the  $\text{H-TiO}_2/\text{CRS}$  interfaces. There is likely to be charging at the contacts when there is a high concentration of NPs  $>10\%$  in the nanocomposite. Furthermore, all three  $\text{H-TiO}_2/\text{CRS}$  nanocomposites show a loss factor  $<0.3$  at  $1$  kHz (Fig. S3†).

#### Conductive atomic force microscopy on $\text{H-TiO}_2/\text{CRS}$ nanocomposite films

Fig. 8 shows topography and current AFM images of  $\text{H-TiO}_2/\text{CRS}$  nanocomposite films. As shown in Fig. 8(a),  $\text{H-TiO}_2$  nanoparticles within the polymer gives rise to topology differences. In the AFM topography image bright spots are ascribed to  $\text{H-TiO}_2$  nanoparticles exposed on the surface. The corres-





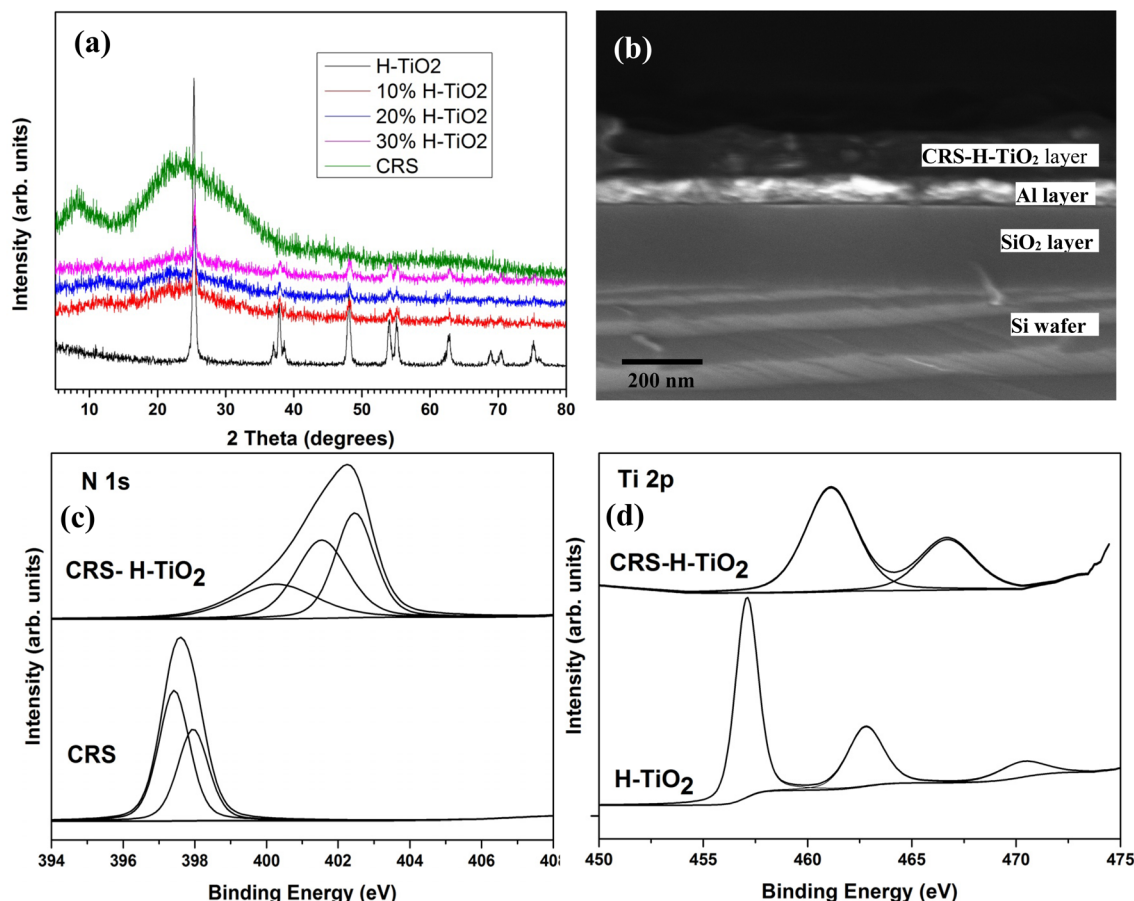

**Fig. 6** (a) PXRD traces, (b) SEM images cross section of a H-TiO<sub>2</sub>/CRS (10%) (c) XPS N 1s spectra for CRS and H-TiO<sub>2</sub>/CRS (d) XPS Ti 2p spectra for H-TiO<sub>2</sub> and H-TiO<sub>2</sub>/CRS (10%) nanocomposite.

ponding current distribution image of H-TiO<sub>2</sub>/CRS nanocomposite is shown in Fig. 8(b). Fig. 8(c) shows overlap of Fig. 8(a) and (b). In addition, Fig. 8(d–g) shows topography, corresponding C-AFM image of current distribution, topography-current image overlaps and IV curve of selected H-TiO<sub>2</sub> agglomerate on the nanocomposite thin film. Fig. 8(h) shows step height of 10% H-TiO<sub>2</sub>/CRS nanocomposite which was used to measure the average film thickness.

In the C-AFM configuration the biasing conditions negative currents are measured, corresponding to dark spots in the C-AFM image. The dark spots in the current image are in the vicinity of H-TiO<sub>2</sub> particles and leakage paths through the nanocomposite are associated with the H-TiO<sub>2</sub> nanoparticles. For a negative potential at the tip, *I*-*V* curve shows typical diode type behaviour between the Pt coated AFM tip and the H-TiO<sub>2</sub> nanoparticle embedded in CRS polymer.

#### Energy band diagram for H-TiO<sub>2</sub>/CRS

Energy band diagram for H-TiO<sub>2</sub> and CRS interface was constructed using the HOMO and LUMO energy levels of H-TiO<sub>2</sub> and pristine CRS polymer extracted using UV/Vis and UPS data as discussed in detail previously in ref. 20. Same as in CRS-

TiO<sub>2</sub> system, band energy levels for CRS are aligned to those of H-TiO<sub>2</sub> as shown in Fig. 9 below.

Though the CRS is an insulator, at the interface with the H-TiO<sub>2</sub> it is shown as having the capability to charge through interaction with defect and polarised bonding states. The interface at equilibrium therefore conforms to a semiconductor heterojunction model. However, when a potential is applied at the terminals and there is a shift from the equilibrium, only states on the H-TiO<sub>2</sub> side of the interface are available for further filling or emptying. The equilibrium situation is taken as frozen-in charge at the interface. Therefore, the CRS acts as an insulator (no charge) away from the interface, while the charge on the H-TiO<sub>2</sub> side of the interface can change. It is this additional charge which has to be balanced at the terminals of the composite dielectric which leads to the increase in the overall relative permittivity of the nanocomposite film.

Surface modification of NPs was used to improve the chemical interactions at the interfaces between nanoparticles and polymer matrix and thereby influence the charge transfer at the interface to tailor the dielectric properties of the nanocomposites. Hydrogenated TiO<sub>2</sub> nanoparticles obtained by H plasma treatments of pristine confirmed the presence titanol






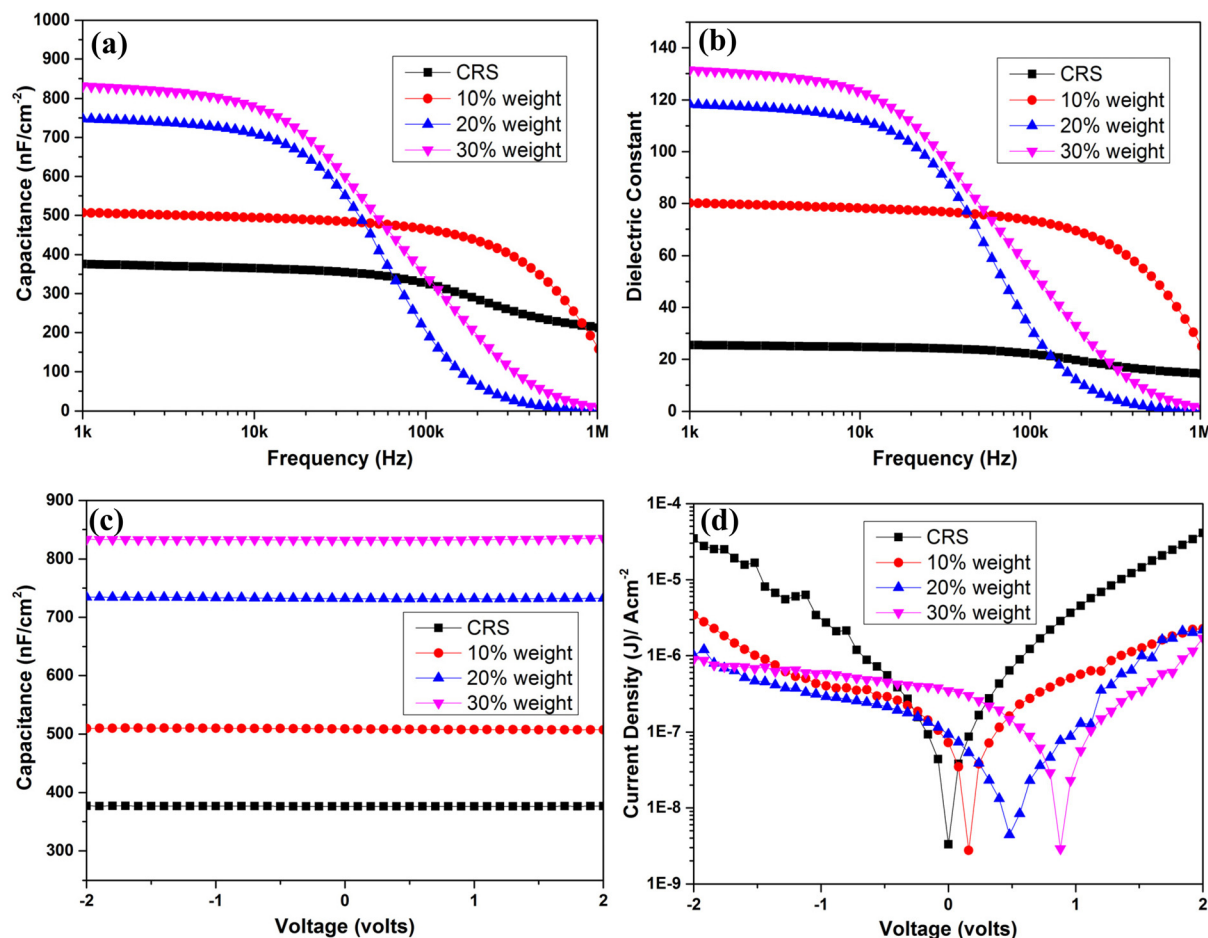


Fig. 7 (a) Capacitance and (b) dielectric constant as a function of frequency and capacitance (c) and current densities (d) as a function of voltage for H-TiO<sub>2</sub>/CRS nanocomposites with different H-TiO<sub>2</sub> loadings.


type functionality on TiO<sub>2</sub> NPs and the surface amorphous nature H-TiO<sub>2</sub>. The pristine TiO<sub>2</sub> NPs with CRS polymer show higher energy densities (At 1 kHz, 80, 118 and 131 dielectric constants extracted were for H-TiO<sub>2</sub>/CRS nanocomposites with 10%, 20% and 30% weight of H-TiO<sub>2</sub> respectively). In the case of TiO<sub>2</sub>/CRS nanocomposites dielectric constants were 118, 176 and 207 with 10%, 20% and 30% weight of TiO<sub>2</sub> respectively). In the case of H-TiO<sub>2</sub>, introduction of titanol type functionality on the TiO<sub>2</sub> surface improves the bonding interactions at the polymer-nanoparticles interface resulting reduced structural mobility. Thus, charging of the interface due to defects from unpaired bond is inhibited. However, capacitance values for H-TiO<sub>2</sub>/CRS nanocomposites in the voltage range of -2 V to 2 V are very stable compared to pristine TiO<sub>2</sub> and CRS nanocomposite. In traditional dielectric composites the highest dielectric constant that can be achieved is always found to be below the dielectric constant of the filler as explained by the logarithmic mixing rule. However, it has been shown that with the introduction of nanosized fillers into polymer matrices significantly higher dielectric constants compared to that of the filler could be achieved. Two

models have been proposed to explain this behaviour, one termed the interface model<sup>10</sup> and the other the multi core model.<sup>32</sup> According to the interface model, the interface zone between the nanoparticle and the polymer has a vital influence on the properties of the dielectric as whole. In the multicore model, dielectric nanoparticles dispersed in a polymer matrix are assumed to result in the formation of different layers termed the bound layer, intermediate layer and the loose layer. The bound layer (1<sup>st</sup> layer) corresponds to the nanoparticle and polymer bonding through functional groups to form an interface which is responsible for the formation of the diffuse electrical double layer. The intermediate layer (2<sup>nd</sup> layer) consists of polymer chains strongly bonded to the bound layer. The loose layer (3<sup>rd</sup> layer) is a region of polymer loosely bound to the second layer. The polarisation phenomena occurring in the interface zones of nanoparticles are proposed as being responsible for ultra-high dielectric constants measured in these dielectric nanocomposites. We propose an extension of this model based on the nanoparticle being a semiconductor which can be internally charge depleted/accumulated to give an increase in the effective dielectric permittivity (constant).



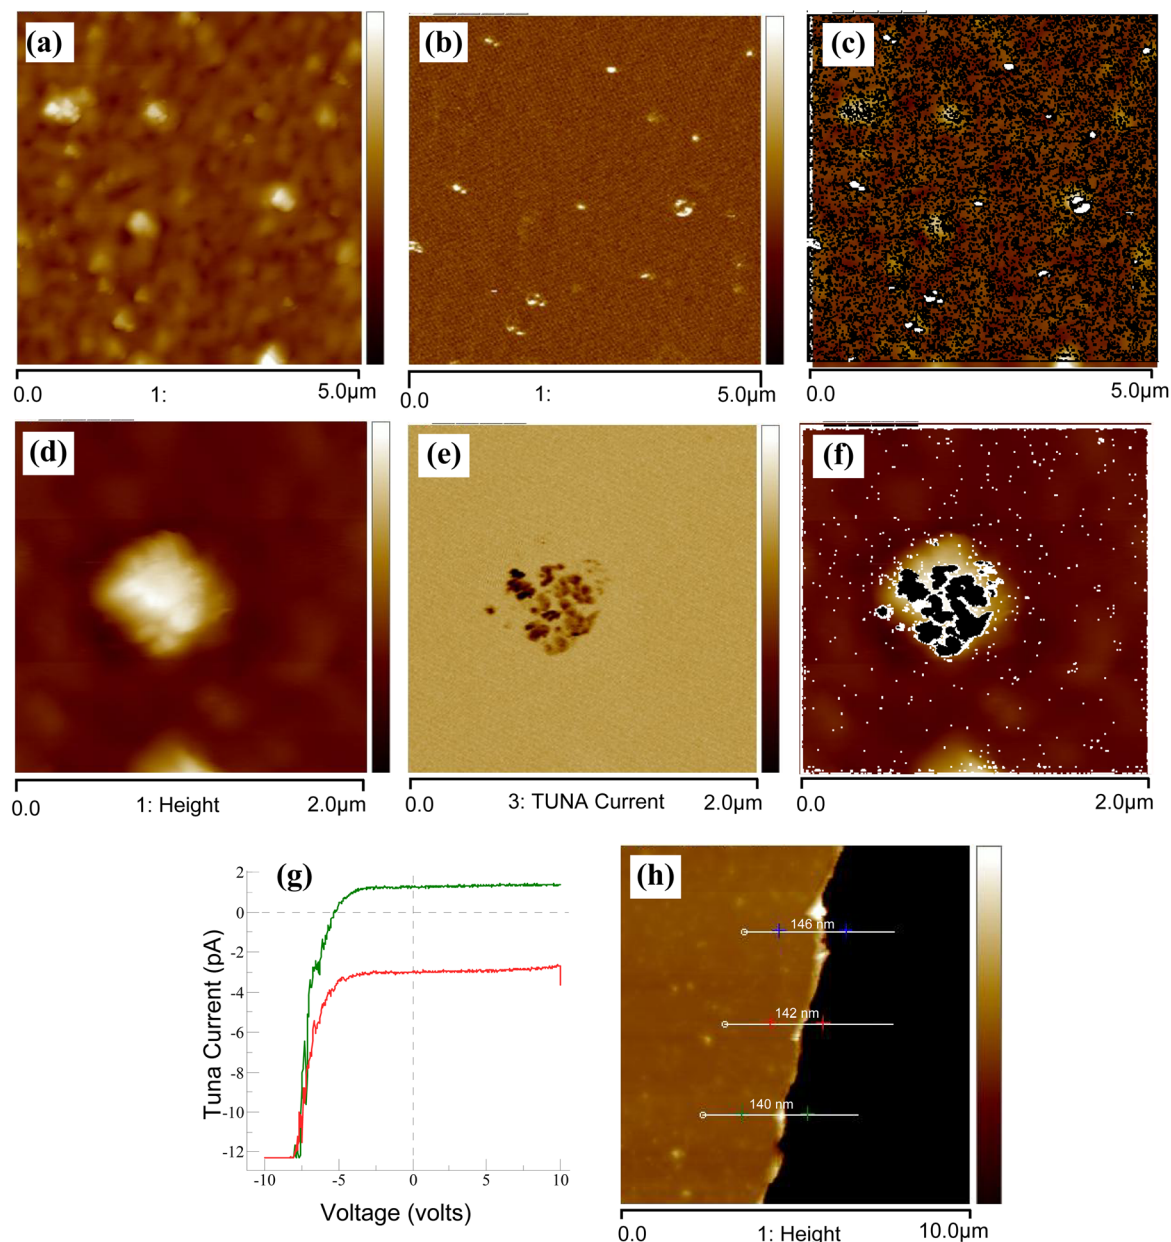

**Fig. 8** (a) Topography image for H-TiO<sub>2</sub>/CRS 10% thin film. (b) Current distribution image for H-TiO<sub>2</sub>/CRS 10% thin film. (c) overlap of topography and current distribution for H-TiO<sub>2</sub>/CRS 10% thin film. (d) Topography image for selected H-TiO<sub>2</sub> agglomerate in H-TiO<sub>2</sub>/CRS 10% thin film. (e) Current distribution for selected H-TiO<sub>2</sub> agglomerate in H-TiO<sub>2</sub>/CRS 10% thin film. (f) Overlap of topography and current distribution selected H-TiO<sub>2</sub> agglomerate in H-TiO<sub>2</sub>/CRS 10% thin film. (g) *IV* curve for selected H-TiO<sub>2</sub> agglomerate in H-TiO<sub>2</sub>/CRS 10% thin film. (h) Step height of H-TiO<sub>2</sub>/CRS 10% thin film.

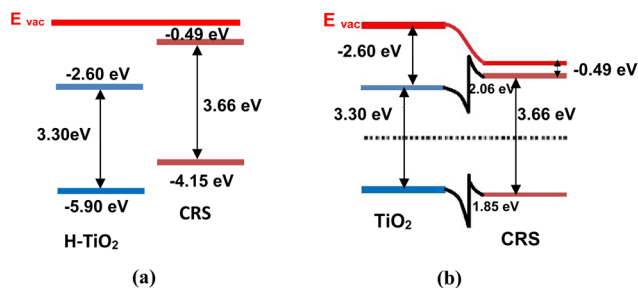

**Fig. 9** Energy band diagram for H-TiO<sub>2</sub>/CRS nanocomposite.

## Conclusions

CRS-H-TiO<sub>2</sub> nanocomposites which exhibit ultra-high dielectric constants 80, 118 and 131 for nanocomposites with 10%, 20% and 30% weight of hydrogenated TiO<sub>2</sub> respectively, significantly higher than values of pure CRS (21) and TiO<sub>2</sub> (41). Furthermore, all three CRS-hydrogenated TiO<sub>2</sub> nanocomposites show a loss factor <0.3 at 1 kHz and low leakage current densities (10<sup>-6</sup> A cm<sup>-2</sup>–10<sup>-7</sup> A cm<sup>-2</sup>). It was observed that the low leakage current is associated with hydrogenated



TiO<sub>2</sub> nanoparticles embedded in the CRS polymer matrix. Although, modified interface slightly reduces energy densities compared to the pristine TiO<sub>2</sub>/CRS system, it increases the stability of capacitance values for H-TiO<sub>2</sub>/CRS in the voltage range of −2 V to 2 V compared to pristine TiO<sub>2</sub>/CRS. The results show that the polymer–nanoparticle interface plays a major role in tuning dielectric properties of the nanocomposite as per the interface model. Also, it was observed that HOMO–LUMO energy alignments between CRS and H-TiO<sub>2</sub> also enhance the polarisation of the nanoscale interfaces which are distributed within the dielectric. The dielectric behavior of nanoscale inorganic dielectrics dispersed in a high permittivity polymer can be tuned *via* modification of the surface properties of inorganic dielectric nanoparticles employing solution free techniques such as hydrogen plasma treatments to obtain electrically stable nanocomposite dielectrics for high energy density capacitors.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was supported by Dyson Research Ltd. NA is also grateful to the Cambridge Commonwealth Trust for financial support and Prof. William Jones, Department of Chemistry, University of Cambridge for providing wet chemical laboratory facilities. Sri Lanka Institute of Nanotechnology (SLINTEC) is acknowledged for providing TEM and solid-state NMR facilities. NA further acknowledges Dr Nuwan de Silva and Dr Dinara Gunasekera for ss-NMR data collection.

## References

- 1 A. P. Arico, P. Bruce, B. Scrosati, J. M. Tarascon and W. V. Schalkwijk, *Nat. Mater.*, 2005, **4**, 366–377.
- 2 G. Yu, X. Xie, L. Pan, Z. Bao and Y. Cui, *Nano Energy*, 2013, **2**, 213–234.
- 3 H. P. Palani, V. Shanmugasundram, E. Jayamani and K. H. Soon, *Renewable Sustainable Energy Rev.*, 2022, **157**, 12075.
- 4 J. C. Pandey and M. Singh, *SPE Polym.*, 2021, **2**, 236–256.
- 5 M. S. Whittingham, *MRS Bull.*, 2008, **33**, 411–419.
- 6 S. P. Culver, C. W. Beier, J. P. Rafson and R. L. Brutchey, *J. Appl. Polym. Sci.*, 2014, **131**, 40290.
- 7 W. Wu, T. Liu, D. Zhang, Q. Sun, K. Cao, J. Zha, Y. Lu, B. Wang, X. Cao, Y. Feng, V. A. L. Roy and R. K. Y. Li, *Composites, Part A*, 2019, **127**, 105650.
- 8 J. J. Xu, C. Fu, H. Chu, X. Wu, Z. Tan, J. Qian, W. Li, Z. Song, X. Ran and W. Ni, *Sci. Rep.*, 2020, **10**, 17084.
- 9 D. Khastgir, H. S. Maiti and P. C. Bandyopadhyay, *Mat. Sci. and Eng.*, 1988, **100**, 245–253.
- 10 T. J. Lewis, *Trans. IEEE*, 1994, **1**, 812–825.
- 11 J. K. Nelson, J. C. Fothergill and L. A. Dissado, *Annu Rep IEEE Conf Electr Insul Dielectr Phen*: 295–298.
- 12 F. C. Chen, C. W. Chu, J. He, Y. Yang and J. L. Lin, *Appl. Phys. Lett.*, 2004, **85**, 3295–3298.
- 13 J. K. Nelson and J. C. Fothergill, *Nanotechnology*, 2004, **15**, 586–595.
- 14 A. Maliakal, H. Katz, P. M. Cotts, S. Subramoney and P. Mirau, *J. Am. Chem. Soc.*, 2005, **127**, 14655–14662.
- 15 R. R. Prakash, S. Pandiarajan, P. Venkatesh and N. Kamaraj, *IEEE*, 2011, **978**, 46–49S.
- 16 J. Li, S. Seok, B. Chu, F. Dogan, Q. Zhang and G. Wang, *Adv. Mater.*, 2009, **21**, 217–221.
- 17 A. Shubha, S. R. Manohara and B. Angadi, *Polym. Bull.*, 2022, **79**, 7117–7135.
- 18 H. Rekik, Z. Ghallabi, I. Royaud, M. Arous, G. Seytre, G. Boiteux and A. Kallel, *Composites, Part B*, 2013, **45**, 1199–1206.
- 19 J. Kim, S. H. Lim and Y. S. Kim, *J. Am. Chem. Soc.*, 2010, **132**, 14721–14723.
- 20 N. Madusanka, S. G. Shivareddy, P. Hiralal, M. D. Eddleston, Y. Choi, R. A. Oliver and G. A. J. Amaratunga, *Nanotechnology*, 2016, **27**, 195402.
- 21 C. K. Chiang and R. Popielarz, *Ferroelectrics*, 2002, **275**, 1–9.
- 22 N. Madusanka, S. G. Shivareddy, M. D. Eddleston, R. A. Oliver and G. A. J. Amaratunga, *Carbohydr. Polym.*, 2017, **172**, 315–321.
- 23 H. He, K. Yang, N. Wang, F. Luo and H. Chen, *J. Appl. Phys.*, 2013, **114**, 213505-5.
- 24 T. Leshuk, R. Parviz, P. Everett, H. Krishnakumar, R. A. Varin and F. Gu, *ACS Appl. Mater. Interfaces*, 2013, **5**, 1892–1895.
- 25 X. Lu, G. Wang, T. Zhai, M. Yu, J. Gan, Y. Tong and Y. Li, *Nano Lett.*, 2012, **12**, 1690–1696.
- 26 Y. Yan, M. Han, A. Konkin, T. Koppe, D. Wang, T. Andreu, G. Chen, U. Vetter, J. R. Morante and F. Schaa, *J. Mater. Chem. A*, 2014, **2**, 12708–12716.
- 27 G. Yang, Z. Jiang, H. Shi, T. Xiao and Z. Yan, *J. Mater. Chem.*, 2010, **65**(20), 5301.
- 28 Y. Sun, Z. Sun, S. Gao, H. Cheng, Q. Liu, J. Piao, T. Yao, C. Wu, S. Hu, S. Wei and Y. Xie, *Nat. Commun.*, 2012, **3**, 1057.
- 29 M. Mehta, N. Kodan, S. Kumar, A. Kaushal, L. Mayrhofer, M. Walter, M. Moseler, A. Dey, S. Krishnamurthy, S. Basu and A. P. Singh, *J. Mater. Chem. A*, 2016, **4**, 2670–2681.
- 30 S. A. Bakar and C. Ribeiro, *J. Photochem. Photobiol., C*, 2016, **27**, 1–29.
- 31 A. K. Jonscher, *J. Phys. D: Appl. Phys.*, 1999, **32**, R57–R70.
- 32 T. Tanaka, M. Kozaroko, N. Fuse and Y. Ohki, *IEEE Trans. Dielectr. Electr. Insul.*, 2005, **12**, 187–196.

