

CrystEngComm

rsc.li/crystengcomm



ISSN 1466-8033

HIGHLIGHT

Meenesh R. Singh *et al.*
Toward dynamic crystal structure prediction: integrating
thermodynamic and kinetic modeling



Cite this: *CrystEngComm*, 2026, 28, 1727

Toward dynamic crystal structure prediction: integrating thermodynamic and kinetic modeling

Prem K. Reddy,[†] Anish V. Dighe,^{ID†}
 Rajan R. Bhawnani^{ID} and Meenesh R. Singh^{ID*}

Precise control over the physical properties of organic molecular crystals is crucial for the design and manufacture of pharmaceutical compounds. Many organic molecules exhibit polymorphism, the ability to exist in multiple solid-state forms, each possessing distinct physical properties such as bioavailability, density, and dissolution rate. These variations are not merely academic; they can render a pharmaceutical compound ineffective or even hazardous if the undesired polymorph forms. Achieving reliable control over polymorphism therefore requires a fundamental understanding of the mechanisms of crystallization and molecular self-assembly spanning from the molecular to the macroscopic scale. Insights into self-assembly at multiple scales offer the opportunity to elucidate the dynamics of weak intermolecular interactions, advancing both crystal engineering and materials design. Existing computational approaches to crystal structure prediction (CSP) primarily focus on identifying dense, energy-minimized packings of molecules within rationally selected space groups. Although such thermodynamic methods can enumerate possible polymorphs, they often fail to consistently reproduce the experimentally observed crystal form under realistic kinetic and solvent conditions. This review aims to establish a conceptual framework for a multiscale model of crystallization, integrating both energetic and kinetic perspectives. By critically assessing the computational methods that model molecular self-assembly, nucleation, and growth, this work outlines a pathway toward dynamic crystal structure prediction, a unified approach capable of predicting not just feasible polymorphs but also the dominant crystal form that emerges under specific crystallization conditions.

Received 13th October 2025,
 Accepted 29th January 2026

DOI: 10.1039/d5ce00977d

rsc.li/crystengcomm

Department of Chemical Engineering, University of Illinois Chicago, 929 W Taylor St, Chicago, IL, 60607, USA. E-mail: mrsingh@uic.edu; Tel: +1 (312) 413 7673

[†] Authors contributed equally.

1. Introduction

1.1. Crystals, characteristics, and properties

Self-assembly of atoms or molecules into periodic structures is central to the formation of a wide variety of inorganic and



Prem K. Reddy

Technology.

Prem K. Reddy received his PhD in Chemical Engineering from the University of Illinois Chicago, under the guidance of Dr. Meenesh Singh. His research focuses on exploring the crystallization of small molecules and metal–organic frameworks through theoretical approaches including molecular dynamics, population balance and microkinetic modeling. He is currently a postdoctoral associate at the Massachusetts Institute of



Anish V. Dighe

processes for small molecules and metal–organic frameworks.

Anish V. Dighe is a Senior Scientist at Merck. He earned his PhD in Chemical Engineering from the University of Illinois Chicago, where he conducted his doctoral research under the supervision of Meenesh R. Singh. He subsequently completed postdoctoral training at the Massachusetts Institute of Technology. His research expertise lies in the mathematical modeling and simulation of crystallization



organic crystalline materials such as semiconductors, catalysts, pharmaceuticals, agrochemicals, biocrystals, adsorbents, inorganic–organic frameworks, food products, and specialty chemicals.^{1–6} The process of forming crystals begins with the self-assembly of molecules in solution to form small clusters, followed by layer-by-layer growth of clusters *via* self-assembly of molecules on their surface.^{7,8} These two stages of crystallization, namely nucleation and growth, are driven by the ordered self-assembly of molecules at different length scales, which collectively determine three primary characteristics – crystal structure (also referred to as polymorph or form), morphology (also referred to as shape), and size.⁵ The other characteristics such as defects, grain boundaries, compositional purity, and chirality, which arise from disordered self-assembly of atoms or molecules, can be important in fields ranging from electronic materials to pharmaceutical solids. The primary characteristics of crystalline materials can affect their physical properties. For example, the stability and bioavailability of pharmaceutical crystals are governed by the polymorph obtained; the activity and selectivity of catalytic reactions depend on the distribution of exposed facets on the catalyst; the band gap of semiconductor crystals varies with morphology and size; and downstream operations such as filtration, drying, and conveying of crystalline particles depend strongly on their aspect ratio. The relationship between crystallization conditions, crystal characteristics, and resulting physical properties is briefly depicted in Fig. 1. The relationship between crystal characteristics and physical properties can be determined from either theory (*e.g.*, molecular simulations, density functional theory, or population balance modeling) or experiments (*e.g.*, X-ray diffraction, atomic force microscopy, or spectroscopy) that are specific to the crystalline material and its application domain.^{9–12}

Several computational models have been developed to predict structure–property relationships for crystalline

materials, such as the Hartman–Perdok theory for morphology prediction, population balance modeling for size distributions, and molecular dynamics or density functional theory (DFT)-based simulations for polymorph stability.^{13–18}

Recent work has further integrated machine learning with these frameworks to predict crystal shapes and lattice energies directly from molecular descriptors, demonstrating rapid and accurate polymorph screening.¹⁹ The primary characteristics that yield desired physical properties can thus be identified from such computationally established characteristics–properties relationships. However, the most difficult task in crystallization remains to reproducibly grow crystals with targeted characteristics under realistic conditions, a challenge that has been central to crystallization research for several decades. This difficulty arises from the high sensitivity of nucleation and growth to supersaturation, solvent interactions, and impurities, making the control of polymorphism and morphology an ongoing pursuit across chemistry, materials science, and process engineering.²⁰

1.2. Crystallization from the bird's-eye view

To tackle such a challenging task, it is of immense importance to understand the process of forming crystals – crystallization – and the physicochemical factors that govern it. Crystallization is one of the most widely employed separation and purification techniques in the chemical and pharmaceutical industries, used to isolate molecules or atoms in a pure solid form.²¹ The process of solution crystallization begins with nucleation (the birth of crystals) followed by crystal growth in a supersaturated solution consisting of solute molecules – the target species to crystallize – solvent molecules – which govern the kinetics of solute transport and attachment – and, in some cases, additives or impurities that modulate molecular interactions to favor or inhibit particular morphologies or polymorphs.²¹



Rajan R. Bhawnani

Rajan R. Bhawnani received his Ph.D. in Chemical Engineering under the guidance of Dr. Meenesh R. Singh from the University of Illinois, Chicago (UIC) with a specialization in porous crystalline materials. He currently is a postdoctoral associate in the chemical engineering department at Massachusetts Institute of Technology (MIT) with Dr. Allan S. Myerson.



Meenesh R. Singh

Meenesh R. Singh is a Professor and Director of the Materials & Systems Engineering Lab at the University of Illinois Chicago. He also holds a Joint Appointment at Argonne National Laboratory and a visiting professorship at the Indian Institute of Technology Roorkee. He received his PhD in Chemical Engineering from Purdue University and then continued his career as a postdoctoral scholar at Lawrence Berkeley National Laboratory and at the University of California, Berkeley. His work is focused on all aspects of materials chemistry and electrochemical energy conversion and storage.





Fig. 1 Relationship between crystallization conditions, primary characteristics and physical properties of crystalline materials.

The degree of supersaturation, defined as the chemical potential difference between solute molecules in the solution and those in equilibrium, serves as the primary driving force for crystallization.²¹ Supersaturation can be generated and controlled by adjusting either the temperature (cooling crystallization) or the solvent composition (antisolvent crystallization), based on the solid-liquid equilibrium (SLE) data (schematic is shown in Fig. 2a).^{22,23} At sufficiently high supersaturation, crystals may nucleate spontaneously within the homogeneous bulk of the solution (known as primary nucleation) or on foreign surfaces or existing particles (heterogeneous or secondary nucleation), as depicted in Fig. 2b.²¹

The maintenance of supersaturation throughout the process ensures a continuous driving force for molecular assembly. As supersaturation increases, the chemical potential of solute molecules rises, enhancing molecular interactions within the solvation shell and promoting

aggregation. When this driving force exceeds the stabilizing solvation interactions, solute molecules self-assemble into clusters.²⁴ Initially, these small aggregates possess higher surface free energy than bulk free energy and are therefore thermodynamically unstable, favoring redissolution. As clusters grow, a critical size is reached where further molecular addition becomes energetically favorable; the formation of this cluster marks the onset of nucleation.^{24,25} Although the initial rate of cluster formation may be lower than its dissociation rate, the persistent supersaturation ensures that aggregation eventually dominates, leading to stable nuclei formation.

Nucleation establishes a structural template for subsequent crystal growth. During growth, the periodic arrangement of molecules evolves, and crystal faces with slower growth rates become dominant in the final morphology. Faces that grow rapidly disappear from the equilibrium shape (morphology, habit, and shape are used



Fig. 2 (a) Representative solid-liquid equilibrium curve showing the relationship between temperature, solute concentration, and the supersaturation region where primary and secondary nucleation occur. (b) Depiction of nucleation and crystal growth.



interchangeably in the literature). It is well established that the level of supersaturation determines the prevailing growth mechanism, such as spiral growth, two-dimensional (2D), or rough growth.²⁶ Controlling crystal growth is crucial because the shape evolution directly influences material performance. For instance, in optical or electronic applications, macroscopic crystals with smooth, defect-free surfaces are desired, whereas in pharmaceutical manufacturing, microscopic crystals with a higher specific surface area provide enhanced dissolution rates and bioavailability.²⁷ Thus, understanding the interplay between supersaturation, nucleation, and growth mechanisms is essential for tailoring crystals with targeted properties across disciplines from materials science to pharmaceutical engineering.

1.3. Molecular view of crystallization

Crystallization is a multiscale process that extends from the molecular level to the macroscopic scale, where the binding and organization of solute molecules underlie the formation of ordered solids. The fundamental step of crystallization is the repeated association of solute molecules through noncovalent interactions such as hydrogen bonding, π - π stacking, van der Waals forces, and electrostatic interactions.²⁸ If we take a black-box perspective, as shown in Fig. 3, the crystallization process can be viewed as a continuous series of association and dissociation events of

solute molecules occurring over different time and length scales. These elementary interactions collectively give rise to distinct stages of crystallization, including pre-nucleation clustering, nucleation, and subsequent crystal growth. The dynamic balance between molecular attachment and detachment governs both the rate and direction of crystal evolution, determining which polymorph or morphology ultimately emerges.²⁹

1.4. Scope of review

While the crystal structure is primarily determined during the early stage of nucleation, the morphology and size of crystals can continue to evolve throughout the growth phase. The evolution of these characteristics depends on several rate-governing processes controlled by the system's chemical composition, temperature, pressure, and interspecies interaction energies (see Fig. 1). For instance, the crystal structure depends on the rate of molecular self-assembly into specific lattices and symmetry groups, while the crystal morphology is determined by the relative growth rates of crystallographic faces, and the crystal size varies approximately linearly with the overall growth rate magnitude.^{30–32} Several theories have been proposed to quantitatively predict crystal-face growth rates.^{33,34} These include models based on lattice geometry, such as the Bravais–Friedel–Donnay–Harker (BFDH) method, surface energetics (the Hartman–Perdok theory), and mechanistic

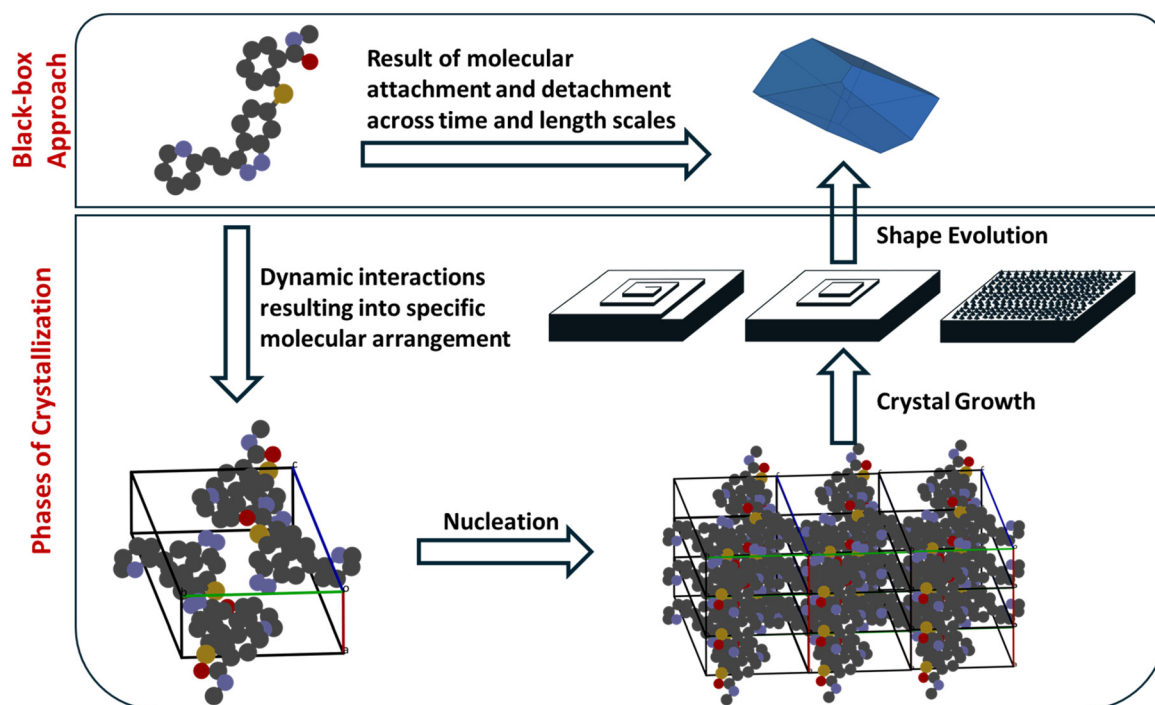


Fig. 3 Two perspectives on the crystallization process. Top: The ‘black-box approach’ representing experimental reality, where often only the initial inputs (supersaturated solution) and final outputs (crystals) are observable, leaving the governing molecular mechanisms obscured. Bottom: The computational goal, which aims to ‘open’ the black box by resolving the process into distinct, modellable phases from molecular self-assembly and nucleation to macroscopic crystal growth, thereby enabling the mechanistic prediction of crystal structure and morphology.



Table 1 List of relevant review articles since 2001 where at least one or more sections are devoted to crystal structure prediction

Authors (year)	Title	Purpose of review
Moulton & Zaworotko ⁴⁷ (2001)	From molecules to crystal engineering: supramolecular isomerism and polymorphism in network solids	To outline challenges and prospects in crystal engineering with a focus on polymers and organic molecules
Vippagunta <i>et al.</i> ⁵³ (2001)	Crystalline solids	Overview of analytical and characterization techniques of polymorphism in pharmaceutical molecules, with a sub-section devoted to prediction of polymorphism
Price S. L. ⁵⁴ (2004)	The computational prediction of pharmaceutical crystal structures and polymorphism	Review of computational structure prediction methods and describing use of computational structure prediction methods to complement characterization of pharmaceutical solids
Datta & Grant ⁵⁵ (2004)	Crystal structures of drugs: advances in determination, prediction, and engineering	Critical review of analytical and computational methods for crystal structure determination
Desiraju G. R. ⁵⁶ (2007)	Crystal engineering: holistic view	Highlight challenges in crystal engineering with focus on crystallization
Woodley & Catlow ⁵⁷ (2008)	Crystal structure prediction from first principles	Rigorous review of computational techniques used in CSP and their application wide areas of chemistry
Price S. L. ¹⁸ (2008)	Computational prediction of organic crystal structures and polymorphism	Review of CSP methodology and discussion on kinetic factors of crystallization
Thakur <i>et al.</i> ⁵⁸ (2015)	Crystal structure and prediction	Review of CSP and describing status of the field
Beran G. J. O. ¹⁷ (2016)	Modeling polymorphic molecular crystals with electronic structure theory	Comprehensive review of use of electronic structure theory for modeling polymorphism with sections devoted to CSP techniques
Graser <i>et al.</i> ⁵⁹ (2018)	Machine learning and energy minimization approaches for crystal structure predictions: a review and new horizons	Computational methods such as DFT and ML are reviewed to CSP, along with the promise and challenges encountered in these techniques
Oganov <i>et al.</i> ⁶⁰ (2019)	Structure prediction drives materials discovery	CSP techniques are reviewed and their potential for the study of different materials systems and new material discoveries
Bowskill <i>et al.</i> ⁶¹ (2021)	Crystal structure prediction methods for organic molecules: state of the art	Reviews methodologies for CSP focused on current research efforts to improve reliability and wide applicability for organic molecules
Yin <i>et al.</i> ⁶² (2022)	Search methods for inorganic materials crystal structure prediction	Highlights the search methods for CSP such as empirical, guided-sampling algorithms, optimization-based search, and data-driven approaches
Clements <i>et al.</i> ⁶³ (2022)	Roles and opportunities for machine learning in organic molecular crystal structure prediction and its applications	Reviews the impact of machine learning CSP and its applications focused on evaluation energies, landscapes, and property-targeted molecule identification
Beran G. J. O. ⁶⁴ (2023)	Frontiers of molecular crystal structure prediction for pharmaceuticals and functional organic materials	Details high-level overview of the CSP methods, current challenges, and case studies for applications

symmetry operations are established, the complete three-dimensional crystal structure can be generated by repeating this motif through those operations. Following Maddox's challenge, researchers began attempting CSP without using diffraction data.^{30,31} For relatively simple molecules, these methods could reproduce experimental structures; however, for more flexible or complex molecules, significant deviations were observed. These discrepancies were attributed to approximations in molecular-potential parameters, and it was hypothesized that improving the accuracy of these potentials would yield experimentally correct crystal structures across diverse systems. Since then, there has been intensive progress in this area. CSP using LEM has not only predicted known polymorphs but has also forecast new, previously unobserved crystal forms, many of which were later confirmed experimentally.^{32–36} This predictive capability has advanced structural chemistry by uncovering insights into conformational flexibility, molecular packing preferences, and the interplay between intramolecular and lattice energetics.^{37–46,50} Modern CSP

approaches now routinely combine lattice-energy minimization with machine-learning-driven energy evaluations and dispersion-corrected quantum-mechanical methods, achieving near-DFT accuracy at a fraction of the computational cost.^{51,52}

Methods for crystal structure prediction (CSP) are aimed at finding the densest and thermodynamically most stable packing arrangements of a molecule that result in minimized lattice energy. The lattice energy represents the sum of intramolecular and intermolecular interactions within the crystal lattice. It is generally hypothesized that, with an accurate description of these interactions, the experimentally observed polymorph will appear among the lowest-energy candidates in a CSP search.⁶⁵ Fig. 5 illustrates the overall workflow of the lattice-energy-minimization (LEM) approach. The process begins with a molecular formula, representing the compound whose crystal structure is to be predicted. The next step is to optimize the three-dimensional geometry of the molecule – typically by quantum-chemical methods (*e.g.*, DFT). These initial stages are relatively easy owing to the wide





Fig. 5 Steps in energy-minimization techniques, corresponding to the key stages of the approach. The first step is to obtain the molecular formula; the second is to optimize the molecular geometry. These are relatively straightforward compared with the third and fourth steps: (iii) generating all possible molecular packings in selected space groups, and (iv) evaluating and ranking based on their energies.

availability of reliable computational tools (Gaussian, ORCA, TURBOMOLE, *etc.*).^{66–68}

The second step is critical because it defines the scope of the conformational search that will be required in subsequent steps. For flexible molecules, it is necessary to identify all possible low-energy conformations in the gas or solvated phase. Once these conformations are determined, one can infer the most probable space groups for crystallization, often guided by statistical analyses of the Cambridge Structural Database (CSD).^{69,70} At this point, the rigid-molecule approximation is commonly applied, assuming that the intramolecular geometry in the gas phase corresponds closely to that in the crystal lattice.⁷¹ This approximation remains valid for small and moderately flexible organic molecules, allowing a major reduction in computational cost without compromising accuracy. The third and fourth steps form the core of LEM-based CSP. After selecting the likely space groups, all possible trial crystal structures (packings) are generated within those symmetry constraints. This search phase may employ random or quasi-random sampling, Monte-Carlo exploration, simulated annealing, or evolutionary algorithms to explore the configurational space efficiently.⁷² The goal is to achieve broad coverage of configurational space while avoiding entrapment in local minima. Recent algorithms increasingly integrate machine-learning-guided or Bayesian optimization strategies to improve sampling efficiency and convergence.^{73,74} For example, a machine-learned force field within an evolutionary CSP framework was used to reproduce all known polymorphs of 66 test molecules with near-DFT accuracy.⁷⁵ Once the candidate structures are generated, the

lattice energy of each packing is computed—this being the most computationally expensive stage of CSP. Each molecule contributes six lattice degrees of freedom (three lattice lengths and three interaxial angles), and the complexity increases exponentially with the number of molecules in the asymmetric unit. Consequently, efficient search and ranking protocols are essential. The resulting structures are rank-ordered by lattice energy, with lower-energy packings representing the most stable polymorph candidates.

For search-space exploration, the third step, the most widely used algorithms include random or quasi-random searches, simulated annealing, Monte-Carlo sampling, evolutionary or genetic algorithms, and molecular-dynamics-based exploration.^{72,76,77} Random and quasi-random searches are undirected methods that often generate a large number of infeasible packings, most of which are quickly rejected due to unrealistic molecular overlaps or density constraints. Simulated-annealing and Monte-Carlo schemes employ stochastic acceptance rules (typically Boltzmann-weighted) that allow occasional uphill steps, helping the search escape local minima.⁷⁸ Evolutionary and genetic algorithms apply biologically inspired operations – mutation, crossover, and selection – to evolve more stable structures iteratively.^{79,80} Hybrid methods combining evolutionary search with Bayesian optimization now represent the state of the art in balancing accuracy and efficiency.⁸¹

Simulated annealing (SA) is a stochastic global-optimization technique used to search for trial crystal structures and was among the first algorithms applied in CSP.^{30,31,82–84} SA is a computational analogue of the physical annealing process in metallurgy. In this method, the





Fig. 6 Timeline of the CCDC blind tests illustrating the evolution of CSP methodologies. The progression highlights the transition from empirical force fields (tests 1–2) to the adoption of DFT for energy ranking (tests 4–5), while the most recent tests (6–7) demonstrate the standardization of dispersion-corrected DFT as the benchmark for stability prediction.

structure was predicted as the global minimum, while the experimentally stable form corresponded to a higher-energy structure (~ 0.5 kJ mol⁻¹ difference) in a different space group.¹²² Such discrepancies revealed that kinetic and entropic effects, often neglected in energy-minimization approaches, can alter polymorph stability. Subsequent blind tests exposed additional limitations – particularly the inadequacy of isotropic force fields in representing anisotropic electrostatics.¹¹⁹ Some participants who succeeded in earlier rounds failed to maintain accuracy in later tests, prompting the CCDC to increase the allowed number of submissions from three to one hundred. This change acknowledged that experimentally observed structures often correspond to kinetically accessible metastable forms, and ranking accuracy must be judged across a broader candidate set. Despite mixed results, the blind tests have driven major advances in methodology, leading to the adoption of dispersion-corrected DFT in modern CSP workflows.¹²³

Accurately modeling weak van der Waals (vdW) interactions is a fundamental requirement for molecular CSP, as these forces frequently dominate the lattice energy. While early semi-local DFT functionals (*e.g.*, PBE) failed to capture these long-range interactions, the development of robust dispersion corrections has effectively resolved this limitation for standard applications. Modern DFT approaches – such as DFT-D3, many-body dispersion (MBD), and hybrid functionals – have successfully integrated both pairwise and higher-order many-body effects into the electronic structure framework and substantially improved accuracy in ranking polymorphs.^{124–126} Fragment-based wave-function methods and ML-assisted DFT energy corrections now represent promising directions for balancing cost and precision.¹¹³ While earlier blind tests revealed challenges with flexible systems and anisotropic electrostatics, the results of the newly concluded seventh blind test (2024) provided a definitive assessment of modern capabilities.^{116,120,121} This test revealed that while generating candidate structures is now considered robust, accurately ranking them remains the

primary challenge. The evaluation demonstrated that DFT incorporating specific dispersion corrections (such as D3, MBD, or XDM) yielded the most consistent results. Conversely, the test highlighted the limitations of ML potentials for final stability determination; while valuable for screening, they frequently struggled to discriminate the subtle energy differences required to identify the global minimum without subsequent DFT refinement. These findings have driven the field toward a consensus workflow: utilizing ML or empirical force fields for broad search, followed by dispersion-corrected DFT for the rigorous final ranking of stability.

Beyond dispersion, a more subtle but equally critical challenge in DFT-based ranking is the inherent ‘delocalization error’ (or self-interaction error) present in some semi-local functionals.¹²⁷ This error can artificially stabilize specific electronic configurations, leading to incorrect energy rankings. This issue is particularly pronounced in conformational polymorphs, where the relative stability of different molecular geometries is sensitive to electron delocalization across conjugate π -systems. A notable example is the highly polymorphic system known as ROY (5-methyl-2-[(2-nitrophenyl)amino]-3-thiophenecarbonitrile). As demonstrated in previous work, standard DFT functionals often fail to reproduce the experimental stability order of ROY polymorphs largely due to errors in predicting the relative energies of the monomer conformations.¹²⁸ Achieving reliable ranking in such challenging cases frequently requires moving beyond standard DFT to incorporating monomer energy corrections derived from second-order Møller–Plesset perturbation theory (MP2), which effectively mitigates the delocalization error.¹²⁹ Thus, for molecular crystals with complex electronic structures, a hierarchical approach—refining DFT rankings with high-level MP2 calculations—is often suggested to ensure accuracy.

A further critical limitation of standard CSP workflows is the reliance on static lattice energies, which correspond to the crystal structure at 0 K without zero-point fluctuations.¹³⁰ In reality, crystallization occurs at finite temperatures where vibrational entropy and thermal expansion play decisive roles



in relative stability. Neglecting these thermal free-energy contributions can result in incorrect ranking, particularly for enantiotropic systems where stability order reverses with temperature. Incorporating these effects requires harmonic (or quasi-harmonic) phonon calculations to estimate the vibrational density of states. However, these calculations are roughly two orders of magnitude more expensive than static energy evaluations, making them computationally prohibitive for all but a few final candidates. Recent work has demonstrated that accurate ranking often requires coupling many-body dispersion effects with rigorous phonon calculations.¹³¹ Similarly, analysis of the 7th blind test highlighted that while dispersion-corrected DFT is robust for static lattices, the absence of thermal corrections remains a major source of uncertainty when predicting experimental forms under ambient conditions.¹²⁰

Energy-minimization-based CSP approaches are limited by their neglect of nucleation kinetics and reliance on approximations to reduce computational expense. As molecular complexity increases, crystallization often becomes kinetically, rather than thermodynamically, controlled.¹³² Under such conditions, ranking polymorphs solely by lattice energy yields incomplete or misleading predictions. Numerous studies have emphasized that incorporating kinetic effects – such as molecular diffusion, solvent interactions, and metastable intermediate states – is essential for realistic CSP.^{48,133–138} Even if future algorithms successfully reproduce all experimentally known polymorphs within the top 100 predicted structures, identifying which polymorph actually forms experimentally will still demand coupling CSP with kinetic modeling and multiscale simulations.^{132,135} Although energy-minimization techniques may not yet fully capture the dynamics of polymorph selection, they remain invaluable for mapping the thermodynamic landscape and identifying potential metastable forms, thus guiding both experiment and process design.

However, despite these advances in ranking accuracy, the field remains challenged by the fundamental ‘over-prediction problem’. CSP landscapes invariably contain many more distinct crystal structures within a thermodynamically accessible energy window (typically $<10 \text{ kJ mol}^{-1}$ from the global minimum) than are ever observed experimentally.¹³⁵ While these predicted structures represent valid local minima on the potential energy surface, the vast majority are never realized in the laboratory. Recent work has demonstrated that this discrepancy is partly due to the neglect of thermal effects; many distinct minima on the 0 K surface are separated by low energy barriers and effectively merge into single vibrational basins at finite temperatures.¹³⁹ By applying threshold clustering algorithms to group these minima, the number of distinct predicted polymorphs can be significantly reduced, aligning predictions closer to experimental reality. However, even after accounting for these thermal basins, the number of energetically feasible structures often exceeds observation. This underscores that

lattice energy minimization provides only a partial picture: it identifies what is thermodynamically possible, but not what is kinetically accessible. The selection of specific polymorphs from this crowded landscape is ultimately governed by the height of nucleation barriers and the rates of crystal growth, necessitating the transition from purely static energy calculations to the dynamic kinetic models discussed in the following sections.

2.2. Kinetic prediction of crystal structure

The ordered assembly of molecular building blocks is a ubiquitous phenomenon underlying diverse materials – from molecular crystals to supramolecular frameworks.¹⁴⁰ Crystallization can be regarded as a self-assembly process operating across multiple time and length scales. The concept of self-assembly is broad, and whether the organization of organic molecules in solution under a strong driving force qualifies as spontaneous “self-assembly” or as a kinetically driven formation process remains debated. In this work, we treat the association of solute molecules in solution as a self-assembly event leading to crystal nucleation.

Modeling molecular self-assembly is crucial because initial aggregation of solute molecules often gives rise to recurring structural motifs called “synthons”.^{56,141} Under specific thermodynamic conditions, only one dominant synthon may form, and this early motif is frequently retained in the crystal lattice – an idea known as the “link hypothesis”, recently validated experimentally for tetrolic acid crystals using *in situ* FTIR spectroscopy.¹⁴² In polymorphic systems, variations in the structure of the early aggregates can dictate which polymorph ultimately appears. Unfortunately, few studies have explicitly connected polymorph selection to early-stage self-assembly, though recent combined experimental-simulation analyses are beginning to close this gap.¹⁴³

Modeling self-assembly involves computing the forces and potential-energy surfaces governing solute-solute and solute-solvent interactions, or mapping the temporal and spatial evolution of the system toward low-energy configurations. Such simulations are computationally intensive and thus limited to short time (10^{-9} – 10^{-6} s) and nanoscale dimensions. They are primarily aimed at capturing the dynamic structure of pre-nucleation aggregates under near-equilibrium conditions. Comprehensive reviews of self-assembly modeling approaches can be found elsewhere.¹⁴⁴

To date, only a few studies have explicitly related polymorphism to initial molecular aggregation. Both employed MD simulations to compute radial distribution functions (RDFs) for solute-solute and solute-solvent pairs in various solvents.¹⁴⁵ One examined 5-fluorouracil (5-FU) and the other tetrolic acid (TTA).^{146,147} Both reached a similar conclusion: polymorph selection is governed by the nature of early molecular aggregates and their solvent-mediated stability. The TTA study further demonstrated that analyzing these interactions could guide the rational design of solvent composition to steer crystallization toward desired



of ritonavir, is driven by the Ostwald rule of stages, where the system initially crystallizes into a kinetically accessible metastable form before eventually converting to the thermodynamic global minimum.^{158,159} Standard nucleation models often fail to predict these events because they focus on the kinetics of the first emerging nucleus rather than the long-term competitive dynamics between forms.

Recent work has highlighted that “late-appearing” polymorphs are often those that are thermodynamically stable but kinetically hindered. A conceptual framework was proposed that differentiates between the energy landscape (thermodynamic stability) and the crystallizability landscape (kinetic accessibility).¹⁵⁷ They suggest that late-appearing stable forms often possess high molecular strain energy in their crystal conformation, which imposes a high kinetic barrier to nucleation even if the lattice energy is favorable. Consequently, a complete CSP workflow must not only rank structures by lattice energy but also assess their “crystallizability”, predicting not just what is stable, but when (or if) it will appear.

From a modeling perspective, capturing these dynamics presents significant computational hurdles. Solution-mediated phase transformation (SMPT)—the primary mechanism for late-appearing polymorphs—occurs over timescales ranging from hours to years, far beyond the nanosecond reach of standard MD. Simulating the transition requires rare-event sampling techniques, such as forward flux sampling (FFS) or metadynamics, to model the dissolution of the metastable form and the concomitant nucleation of the stable phase. Furthermore, the reaction coordinate is often complex, involving not just the order parameter of the new crystal but the explicit interfacial interactions between the dissolving metastable surface and the emerging stable nucleus (cross-nucleation). Without accurate models for these specific interfacial energies and transformation rates, identifying

cases where a stable form exists but is kinetically “silent” remains a frontier challenge for the field.

3. Crystal structure prediction beyond a few lattices

3.1. Kinetic models for nucleation

The nucleus of a crystal is characterized by a cluster of molecules that tends to grow rather than dissociate into solution. The process by which these nuclei form is termed nucleation. Nucleation is traditionally described using classical nucleation theory (CNT), which assumes that (i) the structure of the nucleus is identical to that of the bulk crystal, (ii) the surface tension is independent of curvature and temperature, (iii) the nucleus is incompressible, and (iv) growth occurs *via* sequential addition of single “growth units” or monomers.¹⁶⁰ CNT describes the change in Gibbs free energy (ΔG) as the balance between bulk volumetric and interfacial surface energies. Once a cluster exceeds a critical radius, further addition of molecules reduces its free energy, making the cluster stable – this marks the formation of a nucleus, as depicted in Fig. 8. It is essential to draw a sharp distinction between the ‘self-assembled’ clusters discussed in section 2.2 and the ‘critical nucleus’ defined here. Pre-nucleation clusters generally refer to stable or metastable solute aggregates—potentially amorphous or possessing liquid-like order—that exist in dynamic equilibrium with the solution. In contrast, the critical nucleus represents a thermodynamically unstable transition state at the peak of the free energy barrier (ΔG^*). While CNT assumes the nucleus forms directly with the bulk crystal structure from monomers, the self-assembly perspective aligns more closely with non-classical mechanisms, where stable pre-nucleation clusters serve as precursors that must undergo subsequent densification or structural reordering to reach the critical size and structure required for crystal growth.



Fig. 8 Frameworks of different nucleation theories. The upper path indicate two-step (nonclassical) nucleation, where small amorphous clusters densify into larger crystalline nuclei. The lower path represents monomer-by-monomer addition, characteristic of classical nucleation theory.



To account for the discrete kinetics of molecular attachment, CNT has been extended to the kinetic nucleation theory (KNT) framework, where nucleation is treated as a series of elementary association reactions between growth units.^{8,161–163} In this work, we adopt KNT to describe the temporal evolution of cluster formation. One approach to model the kinetics of nucleation involves solving the unsteady-state differential equation for cluster population dynamics.^{164,165} The analytical solution of this equation, developed in the 20th century, gives the nucleation rate (J) as:

$$J = J_0 \exp\left(-\frac{\Delta G^*}{k_B T}\right) \quad (1)$$

$$J_0 = z\rho_s A_{\text{kin}} \quad (2)$$

where J_0 is the pre-exponential factor, comprising the Zeldovich factor (z), the number of nucleation sites (ρ_s), and the rate of attachment (A_{kin}) of monomers to the cluster. ΔG^* represents the free energy barrier for nucleation. The attachment frequency, which depends on the geometry, concentration, and diffusivity of growth units, is usually estimated from atomistic simulations or empirical kinetic models. An alternative approach derives the rate expression from pairwise molecular potentials, producing an equation similar in form to eqn (1).^{166,167} While elegant, this method is applicable only when an accurate intermolecular potential is available, as the derived rate constants depend sensitively on its functional form and parameterization.

Beyond CNT and KNT, extensive theoretical and experimental evidence now supports two-step or nonclassical nucleation mechanisms, where solute molecules first aggregate into dense, amorphous clusters, followed by structural ordering (densification) into crystalline nuclei.^{168,169} The corresponding free-energy landscape exhibits two barriers – one for cluster formation and another for ordering – each influencing the overall nucleation rate.¹⁷⁰ These models better describe the multi-step kinetics observed in proteins, colloids, and small organic molecules. Recent molecular-dynamics and metadynamics simulations have revealed that such multi-step pathways are prevalent even in simple molecular systems.^{145,171}

3.2. Probabilistic models for nucleation

Probabilistic formulations of nucleation employ the Fokker-Planck equation (FPE) to describe the time evolution of the probability density of observing a cluster of a given size.^{167,172} The FPE can be derived from the master equation for birth-death processes, which balances the rates of cluster growth (birth) and dissolution (death). Expanding this master equation in a Taylor series and truncating at the second order yields a Fokker-Planck-type equation, linking deterministic drift (growth) and stochastic diffusion (fluctuations) in cluster size space.¹⁷³ The solution to the FPE can be obtained numerically using Ito's stochastic differential

equations (SDEs), where an ensemble of simulated trajectories converges to the time-dependent cluster-size distribution.¹⁷⁴ These stochastic frameworks bridge molecular-level kinetics and continuum models by explicitly incorporating fluctuations and non-Markovian effects neglected in classical rate theories. Recent studies combine the Fokker-Planck approach with machine-learning algorithms, allowing efficient and accurate solutions.¹⁷⁵

3.3. Population balance models

Population balance equations (PBEs) are another important class of models applied to study the process of nucleation and growth in crystallization.^{176,177} PBEs originated from Smoluchowski's coagulation equation, which describes the time evolution of particle populations under aggregation and breakage events.¹⁷⁸ PBEs are analogous to traditional transport equations in that they express the change in an internal coordinate (*e.g.*, particle size, volume, or composition) with respect to time and position. In the case of nucleation, this internal coordinate is usually particle size. The solution of PBEs yields the particle-size distribution (PSD) of nuclei or crystals in a crystallizer. Recent studies comparing PBE-based predictions with kinetic rate equations report that both approaches produce comparable accuracy, but PBEs require fewer empirical parameters. Moreover, stochastic extensions of PBEs have been developed to describe fluctuations in cluster populations, enabling the study of the probabilistic nature of nucleation in solutions.

MD simulations, which operate on much shorter time scales, has also been extensively applied to study nucleation mechanisms. Comprehensive reviews of molecular simulations for nucleation are available throughout the literature.^{20,179,180} Because nucleation events often occur within the time scales accessible to MD (typically nanoseconds to microseconds), enhanced-sampling techniques such as metadynamics, umbrella sampling, or forward-flux sampling are required to access rare-event kinetics efficiently.¹⁸¹ These methods allow selectively focusing on key collective variables while disregarding irrelevant motions. In one such study, MD simulations revealed that the mechanism of nucleation changes with cluster size, transitioning from diffuse aggregation to ordered crystal growth as the system crosses the critical nucleus size.¹⁸² The authors identified a non-intuitive reaction coordinate that better captured the nucleation pathway, underscoring the need for data-driven and machine-learning-assisted descriptors to interpret nucleation dynamics.

Modeling nucleation during crystallization primarily aims to predict nucleation rates. If we assume that molecular self-assembly and potential polymorphs are well characterized, then differences in polymorph nucleation rates dictate which crystal form will ultimately dominate. Polymorphs with higher nucleation rates are kinetically favored under given conditions. The essential input in these models is the attachment frequency or attachment free energy barrier for a



growth unit joining the nucleus. All models discussed above – including CNT, KNT, and PBEs – require this attachment frequency, which depends on molecular interactions and supersaturation. PBEs, in particular, require the explicit input of the nucleation rate to compute the resulting particle-size distribution in a crystallizer. Therefore, coupling PBEs with kinetic rate equations has become an active area of research to close the multiscale modeling gap.¹⁸³ Such integrated frameworks enable simulation of entire crystallization processes, from nucleation to growth, under realistic process conditions.

3.4. Crystal growth

The shape and size of crystals profoundly influence their physical and functional properties. In many applications, such as pharmaceuticals, optoelectronics, or catalysis, it is essential to control the final crystal morphology. Shape evolution depends on the growth rate of specific crystal faces: faces with higher growth rates disappear quickly, producing elongated or needle-like morphologies, while slow-growing faces become dominant facets. Controlling these growth rates enables targeted shape design. The crystal-growth phase begins once nuclei have formed and molecules attach to the crystal surface. Historically, models of crystal growth began with geometric and equilibrium approaches. The earliest geometric framework was the Bravais–Friedel–Donnay–Harker (BFDH) model, which proposed that the growth rate of a crystal face is inversely proportional to its interplanar spacing.^{184–186} In contrast, equilibrium models sought the morphology that minimizes total crystal free energy – an assumption valid only when growth kinetics are sufficiently fast to approximate equilibrium. Despite simplifications, the BFDH and equilibrium models laid the foundation for modern crystal growth modeling.¹⁸⁷

The Hartman–Perdok theory, which extended these models, introduced the concept of periodic bond chains (PBCs) to classify crystal faces as flat (F), stepped (S), or kinked (K) depending on the number of PBCs intersecting

the face.^{188–190} Faces containing multiple PBCs have higher bonding periodicity and thus lower surface energy and greater stability. With time, mechanistic models emerged – such as two-dimensional (2D) nucleation, the Burton–Cabrera–Frank (BCF) model, the Chernov bulk-diffusion model, the Winn–Doherty model, and the Monte Carlo-based MONTY algorithm.^{191–194} These frameworks clarified that crystal growth typically proceeds through three primary mechanisms: spiral growth, 2D layer-by-layer nucleation, and rough (continuous) growth, as shown in Fig. 9, depending on the supersaturation regime. The Winn–Doherty model in particular advanced the field by defining the growth-mechanism regimes as functions of supersaturation and interfacial free energy. It predicts that: at low supersaturation, spiral growth dominates; at moderate supersaturation, 2D nucleation prevails; and at high supersaturation, rapid rough growth occurs.¹⁹⁵ Building upon this foundation, subsequent studies have formulated shape-evolution and morphology-prediction models, continuously refined with experimental validation and computational integration.¹⁹⁶

The fundamental mechanisms of crystal growth – particle addition, aggregation, or breakage – are naturally captured by PBEs.^{178,197} The generalized stochastic form of PBEs for particulate systems was extended to describe nucleation and growth processes.¹⁹⁸ Solving PBEs in more than one dimension (because real crystal growth is inherently three-dimensional), however, remains computationally challenging. Common approaches include dimensionality reduction (*via* symmetry or shape assumptions) or variable transformation to measurable quantities, though these can reduce predictive accuracy.¹⁹⁹ Recent advances employ principal component analysis (PCA) and morphological PBEs, which enable solving multidimensional problems by projecting high-dimensional data onto a reduced vector space without losing shape information.²⁰⁰ The method of characteristics has been particularly effective for solving time-dependent PBEs describing facet-specific growth rates. Modern implementations construct morphology sets, graphs, and



Fig. 9 Processes occurring on the surface during crystal growth. Solvated molecules from the bulk solution may attach directly to kink sites or first adsorb and diffuse along the surface. Depending on the level of supersaturation, crystal growth proceeds *via* spiral, 2D nucleation, or rough growth. Transitions between these mechanisms can occur due to surface defects or solvent-mediated effects.



domains, which are then solved using the MorphologyDomain software package.¹⁶

Despite continuous progress, crystal growth modeling remains incomplete. Current models often neglect the thickness and energetics of the solvation shell surrounding the solute molecule. This solvation layer strongly influences the binding energy of growth units on crystal surfaces, particularly under low supersaturation conditions where attachment kinetics are rate-limiting. The Winn–Doherty model, for instance, assumes isotropic binding energy and computes only relative growth rates. Moreover, a single crystal face may host multiple spirals, pits, and surface defects, which are typically neglected in continuum models. Growth mechanisms can also transition between regimes, as shown in Fig. 9, (e.g., from 2D nucleation to rough growth) depending on interfacial or solvent effects, yet the conditions governing such transitions remain poorly understood. Developing a model that can quantitatively capture growth-unit binding and growth-mechanism transitions will require incorporating molecular-scale free-energy calculations – similar to those used in nucleation modeling – into mesoscale and process-scale frameworks. A more comprehensive review and a new model for crystal growth will be the topic for another article.

4. Perspective – multiscale modeling for dynamic crystal structure prediction

Currently, multiple computational approaches can individually model distinct phases of crystallization – from molecular self-assembly to crystal growth. However, predicting the dynamic evolution of crystal structure requires an integrated multiscale framework capable of coupling these phases, as depicted in Fig. 10, under consistent thermodynamic and kinetic formalisms. This proposed framework functions as an information pipeline: it begins with molecular self-assembly, where simulations identify the dominant ‘synthons’ or pre-nucleation clusters that define the available polymorphic pathways. These structural motifs serve as the reaction coordinates for the nucleation phase, where stochastic equations determine the probability flux of specific polymorphs emerging from solution. Finally, these nucleation rates are passed as birth terms to the crystal growth phase, modeled *via* PBEs to predict macroscopic properties. The following paragraphs detail how these disparate scales could be mathematically bridged to achieve dynamic prediction.

The self-assembly phase of crystallization focuses on identifying all feasible polymorphs of a solute molecule. In a specific solvent environment, solute–solute and solute–solvent interactions constrain the molecules to a limited number of low-energy configurations. This was confirmed through MD simulations for systems such as 5-fluorouracil and TTA, where distinct aggregation motifs or synthons

were observed to dictate polymorph outcomes.^{146,147} Each synthon represents the fundamental unit of crystal growth, and its structural identity determines the feasible crystal forms accessible under given operating conditions. Although reliable force-field parameters and diffusivities remain a bottleneck and are rarely available for new molecules, machine learning models are a key research direction. Additional complexity arises from kinetic limitations: some molecules exhibit slow crystal growth due to sluggish diffusion or solvation-shell restructuring. To overcome MD's limited timescale (typically up to microseconds), BD provides an efficient alternative by solving the Langevin equation of motion rather than Newton's second law.²⁰¹ BD models the molecular motion as a balance of drift (deterministic) and diffusive (stochastic) forces:

$$mdv_i = -\beta_r v_r dt - \nabla_r \bar{\Phi}_{12} dt + \beta_r \sqrt{D_r} dW_i(t) \quad (3)$$

where v_i is the velocity of the molecule, m is the molecular mass, β_r is the translational friction factor and D_r is the translational diffusivity and $\bar{\Phi}$ is the mean field potential. For molecules where rotational motion cannot be neglected, the Langevin equation takes the form:

$$Id\omega_i = -\beta_\phi \omega_i dt - (\omega \times I \omega_i) dt + \nabla_\phi \Phi_{12} dt + \beta_\phi \sqrt{D_\phi} dW_i(t) \quad (4)$$

Here $\varphi = [\theta_i \phi_i]^T$ is a vector of polar and azimuthal angles, $I = \text{diag}[I_\theta, I_\phi]$ is the moment of inertia matrix, $\beta_\varphi = \text{diag}[\beta_\theta, \beta_\phi]$ is the diagonal matrix of rotational friction factors and $D = \text{diag}[D_\theta, D_\phi]$ is the diagonal matrix of rotational diffusivities.

BD simulations thus enable longer-timescale exploration of solute-cluster dynamics, capturing key features of diffusive aggregation relevant to pre-nucleation clusters. To characterize orientation and packing differences between polymorphs, a molecular frame of reference must be defined. While radial distribution functions (RDFs) quantify solute–solute interactions, they cannot distinguish between distinct polymorphs. For small organic molecules, a rigid-body approximation is generally valid. A rigid molecule containing M atoms can be described by its internal atomic coordinates a^i relative to its center of mass r . The position of a molecule at any time is given by the center of mass in a fixed Cartesian frame and the relative positions of constituting atoms can be obtained from the polar angle and the azimuthal angle such that:

$$a^i = T[\theta(t), \varphi(t)] a^i(0) \quad (5)$$

$$T[\theta(t), \varphi(t)] = \begin{bmatrix} \cos \theta \cos \varphi & -\cos \theta \sin \varphi & \sin \theta \\ \sin \varphi & \cos \varphi & 0 \\ -\sin \theta \cos \varphi & \sin \theta \sin \varphi & \cos \theta \end{bmatrix}$$

Accurate force-field parameterization remains critical for describing both intra- and intermolecular forces during this phase.



Modeling nucleation is essential for calculating nucleation rates and polymorph selection. This requires evaluation of the free energy of attachment between solute molecules, obtainable from potential-well analyses of solvated and desolvated species.²² Most CSP frameworks treat solvent implicitly or neglect competitive adsorption. Yet solvation dynamics, hydrogen-bonding rearrangements, and impurity incorporation strongly influence nucleation kinetics and facet-specific growth rates. Although detailed protocols for calculating attachment energies will be the topic of another article, once these energy barriers are known, nucleation can be treated stochastically using FPE coupled with the Langevin drift terms. During crystallization under supersaturation, drift terms dominate over diffusive terms in the Langevin equation, indicating that deterministic molecular attachment

prevails over random motion. The probability density function of molecular configurations $P(n,t)$ can thus be described by the FPE, allowing computation of time-dependent distributions of pre-nucleation synthons. Each polymorph corresponds to a distinct set of radial and angular coordinates. For a fixed number of solute molecules within the simulation volume, this approach can be used to estimate the population distribution of competing polymorphic clusters in solution.

To analyze which self-assembled structures lead to nucleation, it is necessary to define an internal coordinate that connects the molecular-level cluster evolution with the macroscopic nucleation process. This internal coordinate can be chosen as the particle number (n) or cluster size, which evolves according to:



Fig. 10 Schematic representation of the multiscale computational framework for modeling crystallization. The workflow illustrates the transition from individual molecules to bulk crystals for three distinct polymorphs (I, II, and III). The process integrates molecular dynamics (to identify feasible polymorphs, activation barriers, and attachment energies), Brownian dynamics and Fokker-Planck equations (for longer timescale exploration, capture nucleation events and solute-solvent dynamics), and population balance equations (to predict macroscopic crystal properties). Information flow from one state to another is represented with blue arrows.



- structure methods, *Chem. Rev.*, 2016, **116**(9), 5105–5154.
- 127 K. R. Bryenton, A. A. Adeleke, S. G. Dale and E. R. Johnson, Delocalization error: The greatest outstanding challenge in density-functional theory, *Wiley Interdiscip. Rev.: Comput. Mol. Sci.*, 2023, **13**(2), e1631.
- 128 G. J. Beran, I. J. Sugden, C. Greenwell, D. H. Bowskill, C. C. Pantelides and C. S. Adjiman, How many more polymorphs of ROY remain undiscovered, *Chem. Sci.*, 2022, **13**(5), 1288–1297.
- 129 G. J. Beran, C. Greenwell, C. Cook and J. Rezac, Improved description of intra- and intermolecular interactions through dispersion-corrected second-order Møller–Plesset perturbation theory, *Acc. Chem. Res.*, 2023, **56**(23), 3525–3534.
- 130 G. B. Correa, S. Konstantinopoulos, B. I. Tan, Y. Zhang, F. W. Tavares, C. S. Adjiman and E. J. Maginn, Assessing Polymorph Stability and Phase Transitions at Finite Temperature: Integrating Crystal Structure Prediction, Lattice Dynamics, and Molecular Dynamics, *J. Chem. Theory Comput.*, 2025, **21**(23), 12197–12213.
- 131 A. M. Reilly and A. Tkatchenko, Role of dispersion interactions in the polymorphism and entropic stabilization of the aspirin crystal, *Phys. Rev. Lett.*, 2014, **113**(5), 055701.
- 132 C. Parks, A. Koswara, F. DeVilbiss, H.-H. Tung, N. K. Nere, S. Bordawekar, Z. K. Nagy and D. Ramkrishna, Solubility curves and nucleation rates from molecular dynamics for polymorph prediction—moving beyond lattice energy minimization, *Phys. Chem. Chem. Phys.*, 2017, **19**(7), 5285–5295.
- 133 R. M. Bhardwaj, L. S. Price, S. L. Price, S. M. Reutzel-Edens, G. J. Miller, I. D. H. Oswald, B. F. Johnston and A. J. Florence, Exploring the Experimental and Computed Crystal Energy Landscape of Olanzapine, *Cryst. Growth Des.*, 2013, **13**(4), 1602–1617, DOI: [10.1021/cg301826s](https://doi.org/10.1021/cg301826s).
- 134 T. Beyer, T. Lewis and S. L. Price, Which organic crystal structures are predictable by lattice energy minimisation?, *CrystEngComm*, 2001, **3**(44), 178–212, DOI: [10.1039/b108135g](https://doi.org/10.1039/b108135g).
- 135 S. L. Price, Why don't we find more polymorphs?, *Acta Crystallogr., Sect. B: Struct. Sci., Cryst. Eng. Mater.*, 2013, **69**(4), 313–328, DOI: [10.1107/s2052519213018861](https://doi.org/10.1107/s2052519213018861).
- 136 S. Z. Ismail, C. L. Anderton, R. C. B. Copley, L. S. Price and S. L. Price, Evaluating a Crystal Energy Landscape in the Context of Industrial Polymorph Screening, *Cryst. Growth Des.*, 2013, **13**(6), 2396–2406, DOI: [10.1021/cg400090r](https://doi.org/10.1021/cg400090r).
- 137 P. G. Karamertzanis, A. V. Kazantsev, N. Issa, G. W. A. Welch, C. S. Adjiman, C. C. Pantelides and S. L. Price, Can the Formation of Pharmaceutical Cocrystals Be Computationally Predicted? 2. Crystal Structure Prediction, *J. Chem. Theory Comput.*, 2009, **5**(5), 1432–1448, DOI: [10.1021/ct8004326](https://doi.org/10.1021/ct8004326).
- 138 R. K. Hylton, G. J. Tizzard, T. L. Threlfall, A. L. Ellis, S. J. Coles, C. C. Seaton, E. Schulze, H. Lorenz, A. Seidel-Morgenstern, M. Stein and S. L. Price, Are the Crystal Structures of Enantiopure and Racemic Mandelic Acids Determined by Kinetics or Thermodynamics?, *J. Am. Chem. Soc.*, 2015, **137**(34), 11095–11104, DOI: [10.1021/jacs.5b05938](https://doi.org/10.1021/jacs.5b05938).
- 139 P. W. Butler and G. M. Day, Reducing overprediction of molecular crystal structures via threshold clustering, *Proc. Natl. Acad. Sci. U. S. A.*, 2023, **120**(23), e2300516120.
- 140 G. M. Whitesides and B. Grzybowski, Self-assembly at all scales, *Science*, 2002, **295**(5564), 2418–2421.
- 141 G. R. Desiraju, Supramolecular Synthons in Crystal Engineering—A New Organic Synthesis, *Angew. Chem., Int. Ed. Engl.*, 1995, **34**(21), 2311–2327, DOI: [10.1002/anie.199523111](https://doi.org/10.1002/anie.199523111).
- 142 S. Parveen, R. J. Davey, G. Dent and R. G. Pritchard, Linking solution chemistry to crystal nucleation: the case of tetrolic acid, *Chem. Commun.*, 2005(12), 1531, DOI: [10.1039/b418603f](https://doi.org/10.1039/b418603f).
- 143 A. E. Van Driessche, N. Van Gerven, P. H. Bomans, R. R. Joosten, H. Friedrich, D. Gil-Carton, N. A. Sommerdijk and M. Sleutel, Molecular nucleation mechanisms and control strategies for crystal polymorph selection, *Nature*, 2018, **556**(7699), 89–94.
- 144 R. C. Bernardi, M. C. R. Melo and K. Schulten, Enhanced sampling techniques in molecular dynamics simulations of biological systems, *Biochim. Biophys. Acta, Gen. Subj.*, 2015, **1850**(5), 872–877, DOI: [10.1016/j.bbagen.2014.10.019](https://doi.org/10.1016/j.bbagen.2014.10.019).
- 145 A. V. Dighe, P. Coliaie, P. K. R. Podupu and M. R. Singh, Selective desolvation in two-step nucleation mechanism steers crystal structure formation, *Nanoscale*, 2022, **14**(5), 1723–1732, DOI: [10.1039/D1NR06346D](https://doi.org/10.1039/D1NR06346D).
- 146 S. Hamad, C. Moon, C. R. A. Catlow, A. T. Hulme and S. L. Price, Kinetic Insights into the Role of the Solvent in the Polymorphism of 5-Fluorouracil from Molecular Dynamics Simulations, *J. Phys. Chem. B*, 2006, **110**(7), 3323–3329, DOI: [10.1021/jp055982e](https://doi.org/10.1021/jp055982e).
- 147 J. Chen and B. L. Trout, Computational Study of Solvent Effects on the Molecular Self-Assembly of Tetrolic Acid in Solution and Implications for the Polymorph Formed from Crystallization, *J. Phys. Chem. B*, 2008, **112**(26), 7794–7802, DOI: [10.1021/jp7106582](https://doi.org/10.1021/jp7106582).
- 148 K. Z. Takahashi, T. Aoyagi and J.-i. Fukuda, Multistep nucleation of anisotropic molecules, *Nat. Commun.*, 2021, **12**(1), 5278.
- 149 R. Wang, S. Mehdi, Z. Zou and P. Tiwary, Is the local ion density sufficient to drive NaCl nucleation from the melt and aqueous solution?, *J. Phys. Chem. B*, 2024, **128**(4), 1012–1021.
- 150 D. Zahn, Thermodynamics and kinetics of prenucleation clusters, classical and non-classical nucleation, *ChemPhysChem*, 2015, **16**(10), 2069–2075.
- 151 A. Rojnuckarin, S. Kim and S. Subramaniam, Brownian dynamics simulations of protein folding: Access to milliseconds time scale and beyond, *Proc. Natl. Acad. Sci. U. S. A.*, 1998, **95**(8), 4288–4292, DOI: [10.1073/pnas.95.8.4288](https://doi.org/10.1073/pnas.95.8.4288).
- 152 D. E. Makarov and H. Metiu, A model for the kinetics of protein folding: Kinetic Monte Carlo simulations and analytical results, *J. Chem. Phys.*, 2002, **116**(12), 5205–5216, DOI: [10.1063/1.1450123](https://doi.org/10.1063/1.1450123).
- 153 P. Mereghetti, R. R. Gabdoulline and R. C. Wade, Brownian Dynamics Simulation of Protein Solutions: Structural and



- fluidized bed melt granulation: an overview, *Chem. Eng. Res. Des.*, 2005, **83**(7), 871–880.
- 184 A. Bravais, *Etudes cristallographiques*, Gauthier-Villars, 1866.
- 185 M. G. Friedel, Études Sur la loi de Bravais, *Bull. Soc. Fr. Mineral.*, 1907, **9**, 326–455.
- 186 J. Donnay and D. Harker, A new law of crystal morphology extending the law of Bravais, *Am. Mineral.*, 1937, **22**(5), 446–467.
- 187 A. V. Dighe, P. K. Podupu, V. V. Gande, U. Diwekar and M. R. Singh, Group contribution method for rapid estimation of crystal growth rates, *Chem. Eng. Res. Des.*, 2024, **203**, 140–148.
- 188 P. Hartman and P. Bennema, The attachment energy as a habit controlling factor, *J. Cryst. Growth*, 1980, **49**(1), 145–156, DOI: [10.1016/0022-0248\(80\)90075-5](https://doi.org/10.1016/0022-0248(80)90075-5).
- 189 P. Hartman, The attachment energy as a habit controlling factor, *J. Cryst. Growth*, 1980, **49**(1), 166–170, DOI: [10.1016/0022-0248\(80\)90077-9](https://doi.org/10.1016/0022-0248(80)90077-9).
- 190 P. Hartman, The attachment energy as a habit controlling factor II. Application to anthracene, tin tetraiodide and orthorhombic sulphur, *J. Cryst. Growth*, 1980, **49**(1), 157–165, DOI: [10.1016/0022-0248\(80\)90076-7](https://doi.org/10.1016/0022-0248(80)90076-7).
- 191 W. Burton, N. Cabrera and F. Frank, The growth of crystals and the equilibrium structure of their surfaces, *Philos. Trans. R. Soc., A*, 1951, 299–358.
- 192 A. Chernov, The spiral growth of crystals, *Phys.-Usp.*, 1961, **4**(1), 116–148.
- 193 D. Winn and M. F. Doherty, A new technique for predicting the shape of solution-grown organic crystals, *AIChE J.*, 1998, **44**(11), 2501–2514, DOI: [10.1002/aic.690441117](https://doi.org/10.1002/aic.690441117).
- 194 S. Boerrigter, G. Josten, J. Van De Streek, F. Hollander, J. Los, H. Cuppen, P. Bennema and H. Meekes, MONTY: Monte Carlo crystal growth on any crystal structure in any crystallographic orientation; application to fats, *J. Phys. Chem. A*, 2004, **108**(27), 5894–5902.
- 195 D. Winn and M. F. Doherty, Modeling crystal shapes of organic materials grown from solution, *AIChE J.*, 2000, **46**(7), 1348–1367.
- 196 C. J. Tilbury and M. F. Doherty, Modeling layered crystal growth at increasing supersaturation by connecting growth regimes, *AIChE J.*, 2017, **63**(4), 1338–1352.
- 197 D. Ramkrishna and M. R. Singh, Population balance modeling: Current status and future prospects, in *Annual Review of Chemical and Biomolecular Engineering*, Annual Reviews Inc., 2014, vol. 5, pp. 123–146.
- 198 E. L. Haseltine, D. B. Patience and J. B. Rawlings, On the stochastic simulation of particulate systems, *Chem. Eng. Sci.*, 2005, **60**(10), 2627–2641.
- 199 W. Heineken, D. Flockerzi, A. Voigt and K. Sundmacher, Dimension reduction of bivariate population balances using the quadrature method of moments, *Comput. Chem. Eng.*, 2011, **35**(1), 50–62.
- 200 X. Z. Wang and C. Y. Ma, Morphological population balance model in principal component space, *AIChE J.*, 2009, **55**(9), 2370–2381.
- 201 A. V. Dighe, P. K. Podupu and M. R. Singh, Emulsification of Supersaturated Solutions Amplifies Induction Time Variation in Crystallization, *Cryst. Growth Des.*, 2023, **23**(9), 6290–6297.
- 202 J. Kuipers and G. Barkema, Limitations of a Fokker-Planck description of nucleation, *Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys.*, 2010, **82**(1), 011128.
- 203 E. Komp, N. Janulaitis and S. Valteau, Progress towards machine learning reaction rate constants, *Phys. Chem. Chem. Phys.*, 2022, **24**(5), 2692–2705.

