

Energy Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: L. Gong, S. Zhao, J. Yu, J. Li, J. Arbiol, T. Kallio, M. Calcabrini, P. R. Martínez-Alanisa, M. Ibañez and A. Cabot, *Energy Adv.*, 2024, DOI: 10.1039/D4YA00334A.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

ARTICLE

Influence of the catalyst surface chemistry on the electrochemical self-coupling of biomass-derived benzaldehyde into hydrobenzoin

Li Gong^{a,b}, Shiling Zhao^c, Jing Yu^{a,d}, Junshan Li^e, Jordi Arbiol^{d,h}, Tanja Kallio^f, Mariano Calcabrini^g, Paulina R. Martínez-Alanis^{a*}, Maria Ibáñez^g, Andreu Cabot^{a,h*}9 Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

The electroreduction of biomass-derived benzaldehyde (BZH) provides a potentially cost-effective route to produce benzyl alcohol (BA). This reaction competes with the electrochemical self-coupling of BZH to hydrobenzoin (HDB), which holds significance as a biofuel. Herein, we demonstrate the selectivity towards one or the other product strongly depends on the surface chemistry of the catalyst, specifically on its ability to adsorb hydrogen, as showcased with Cu₂S electrocatalysts. We particularly analyze the effect of surface ligands, oleylamine (OAm), on the selective conversion of BZH to BA or HDB. The effect of the electrode potential, electrolyte pH, and temperature are studied. Results indicate that bare Cu₂S exhibits higher selectivity towards BA, while OAm-capped Cu₂S promotes HDB formation. This difference is explained by the competing adsorption of protons and BZH. During the BZH electrochemical conversion, electrons first transfer to the C in the C=O group to form a ketyl radical. Then the radical either couples with surrounding H⁺ to form BA or self-couple to produce HDB, depending on the H⁺ availability that is affected by the electrocatalyst surface properties. The presence of OAm inhibits the H adsorption on the electrode surface therefore reducing the formation of high-energy state H_{ad} and its combination with ketyl radicals to form BA. Instead, the presence of OAm promotes the outer sphere reaction for obtaining HDB.


1. Introduction

Addressing the environmental crisis requires a transition to clean and zero-carbon energies in both supply and consumption, as well as the adoption of sustainable and efficient chemical synthesis methods.^{1, 2} Electrocatalysis plays a crucial role by allowing precise control over reaction conditions and promoting the use of mild, sustainable, and energy-efficient processes.³⁻¹⁰ This approach enables the fine-tuning of reaction products through adjustable parameters, such as the electrode potential and current density, facilitating the eco-friendly synthesis of complex molecules with unprecedented efficiency.¹¹⁻¹³ In particular, the electrocatalytic reduction of organic compounds is a field of significant interest with broad application potential.


Despite the high economic potential and clean characteristics of electrocatalytic organic reduction processes, their industrial application in the valorization of biomass-derived feedstocks is not widely extended. This is due to their notable complexity and challenging optimization, which arises from the intricate nature of organic compounds and the involvement of multi-step

electron transfer mechanisms and various intermediates. As an example in this direction, the electroreduction of biomass-derived benzaldehyde (BZH) provides a fascinating route for the selective production of benzyl alcohol (BA), a versatile compound widely utilized in the pharmaceutical and fine chemical industries.¹⁴⁻¹⁶ Moreover, the electrochemical self-coupling of BZH to hydrobenzoin (HDB) holds significance as a potential biofuel production route.^{17,18} Both processes, the production of BA and HDB occurring at around 0 V vs. RHE, compete with the hydrogen evolution reaction (HER, 0 V vs. RHE). As shown in Scheme 1, the first elementary step in both reactions involves the protonation of C=O in BZH, which facilitates the posterior acquisition of one electron from the electrode to form a radical intermediate.¹⁸⁻²⁰


In acid media:



In alkaline media:



After the protonation and electron transfer steps, either the dimerization of two radicals in solution to produce HDB or the combination of the radical with an adsorbed hydrogen (H_{ad}) in a Langmuir-Hinshelwood (L-H) scheme to obtain BA takes place. While the electroreduction of BZH to HDB is an outer-sphere reaction, i.e. does not involve surface adsorption,²¹⁻²⁵ BA production depends on the H_{ad} availability on the catalyst surface:



a*. Catalonia Institute for Energy Research – IREC Sant Adrià de Besòs, Barcelona 08930, Spain E-mail: pmartinez@irec.cat, acabot@irec.cat

b. University of Barcelona, Barcelona 08028, Spain.

c. School of Petrochemical Engineering, Lanzhou University of Technology, Lanzhou, 730050, China.

d. Catalan Institute of Nanoscience and Nanotechnology (ICN2), CSIC and BIST, Campus UAB, Bellaterra, 08193, Barcelona, Spain.

e. Institute of Advanced Study, Chengdu University, Chengdu, 610106, China

f. Department of Chemistry and Materials Science, Aalto University School of Chemical Engineering, P.O. Box 16100, FI-00076 Aalto, Finland.

g. IST Austria, Am Campus 1, Klosterneuburg, 3400 Austria

h. ICREA, Pg. Lluís Companys 23, 08010, Barcelona, Spain


Supplementary Information available: See DOI: 10.1039/x0xx00000x



In alkaline media: $\text{H}_2\text{O} + e^- + * \rightarrow * \text{H} + \text{OH}^-$

where * represents an adsorption site. Both in acid and basic conditions, the selective production of HDB requires reducing the amount of H_{ad} to reduce the formation of BA.

To maximize HDB selectivity, current catalyst design strategies primarily focus on materials with high HER overpotentials such as Hg, Pb, In, and Cd.^{22, 26-29} However, beyond concerns of metal toxicity and cost, this strategy has intrinsic limitations. Increasing the negative voltage or temperature to accelerate the reaction raises the Fermi level on the catalyst surface, resulting in more adsorbed hydrogen protons concentrating on the solution side of the electrical double layer (EDL). This, in turn, promotes the hydrogenation of ketyl radicals leading to the formation of BA.

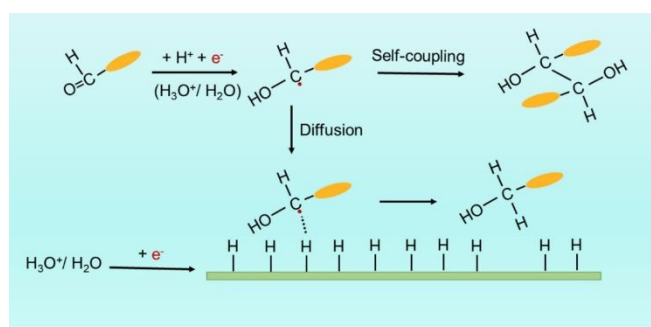

Scheme 1. Two pathways for the BZH electroreduction, to BA or HDB. The orange ellipsoid represents the benzene ring. Red spots represent electrons provided by the electrode that is represented here by a green bar.

Beyond material selection, the rational design and engineering of the catalyst surface chemistry is a powerful strategy to promote selectivity. More specifically, the modification of the electronic energy levels of the catalyst surface using functional groups such as -OH and -SOOH,^{30, 31} as well as larger organic groups such as aromatic thiols, have been shown to favor specific reaction mechanisms.³²⁻³⁴ Besides modifying the electronic energy levels, the presence of surface species can also adjust selectivity by tailoring the surface adsorption properties. As an example, lipophilic species can enhance the gathering of organic substances at the catalyst surface. In this direction, Baik's group demonstrated an increase in selectivity by promoting the Suzuki-Miyaura cross-coupling reaction with organic monolayers self-assembled at the electrode surface.³⁵ Besides, Li's group tailored the interfacial environments of Pb electrodes using quaternary alkyl ammonium cations to control the selectivity of BZH to BA or HDB. They showed that the longer the chain length and the higher the cation concentration, the higher the selectivity towards HDB.²⁶

Herein, we modify the surface of Cu_2S nanoparticles (NPs) by adding a monolayer of unsaturated fatty amines, specifically oleylamine (OAm), and explore its effect on the electrocatalytic conversion of BZH to either BA or HDB. Cu was selected taking into account its exceptional ability for radical generation.²⁷ We investigate the effect of voltage and temperature on the reaction selectivity at pH 5.2 and pH 9.0. We further explore the involved electroreduction reaction pathways aiming to unveil the rate-determining steps and gain insight into the parameters determining the reaction selectivity. Our final goal is to enable a more rational design of electrocatalyst for the selective electroreduction of biomass-derived BZH.

2. Experimental

View Article Online

DOI: 10.1039/D4YA00334A

2.1 Materials.

Copper(II) acetylacetonate ($\text{Cu}(\text{acac})_2$, Sigma Aldrich, 97%), oleylamine (OAm, Aladdin Reagent, 70%), dodecanethiol (DDT, Sigma Aldrich, 98%), *N,N*-dimethylformamide (DMF, Sigma Aldrich, anhydrous, 99.8%), methanol (CH_3OH , 96%, Letslab), ethanol ($\text{CH}_3\text{CH}_2\text{OH}$, 96%, Letslab), benzaldehyde ($\text{C}_7\text{H}_6\text{O}$, Sigma Aldrich), benzyl alcohol ($\text{C}_7\text{H}_8\text{O}$, Sigma Aldrich), benzoic acid ($\text{C}_7\text{H}_6\text{O}_2$, Sigma Aldrich), and hydrobenzoin ($\text{C}_{14}\text{H}_{14}\text{O}_2$, Sigma Aldrich) were used as purchased, without further purification.

2.2. Cu_2S preparation.

Cu_2S NPs were produced following a modified version of a previously reported procedure.³⁵ Briefly, in a three-neck flask equipped with a reflux condenser, a mixture of $\text{Cu}(\text{acac})_2$ (1.56 g, 0.6 mmol), DDT (20 mL), and OAm (40 mL) was deaerated with nitrogen at 120 °C for 20 min. After the nitrogen purging step, the mixture exhibited a light brownish-yellow color. Then, the solution was heated to 200 °C at a constant heating rate of 8 °C min⁻¹ and kept at this temperature for 60 min. During this time, the solution becomes turbid, and the color deepens to a brown-black indicating the occurrence of the chemical reaction. Then, the mixture was cooled down to room temperature. The material was washed with hexane/methanol, separated by centrifugation (9000 rpm, 10 min), and finally dispersed in hexane.

2.3 Ligands removal.

The ligands used to control the Cu_2S NP growth were removed using an annealing step.³⁶ The dried Cu_2S NP powder was annealed for 2 h under an Ar flow inside a tube furnace at 400 °C, reached using a heating rate of 10 °C min⁻¹.

2.4 Materials Characterization.

High-resolution transmission electron microscopy (HRTEM) and high-angle annular dark field (HAADF) images were acquired in a Tecnai F20 microscope operated at 200 kV. Energy dispersive spectroscopy (EDS) spectra were obtained in a double-corrected and monochromated Thermo Fisher Spectra 300 microscope operated at 200 kV. Powder X-ray diffraction (XRD) patterns were collected at 40 kV and 40 mA with $\text{Cu K}\alpha$ radiation ($\lambda = 1.5406 \text{ \AA}$). Fourier-transformed infrared (FT-IR) spectra of the unsupported samples were recorded on an Alpha Bruker spectrometer. X-ray photoelectron spectroscopy (XPS) was conducted on a ThermoFisher (ESCALAB 250Xi) system with Mono Al $\text{K}\alpha$ radiation. The vacuum of the analysis chamber was approximately 2×10^{-9} mbar. The energy, voltage, and beam current were 1486.6 eV, 16 kV, and 15 mA, respectively. XPS spectra were corrected to the position of the C 1s peak at 284.6 eV.

2.5 Product identification and conversion and selectivity quantification.

High-performance liquid chromatography (HPLC) analysis of the organics was carried out on an Agilent 1200 series apparatus at 25 °C. The HPLC was equipped with an ultraviolet-visible detector and a 4.6 mm \times 150 mm Shim-pack GWS 5 μm C18 column. The eluting solvents of A: 5 mM ammonium formate aqueous solution; and solution B: acetonitrile was used. The program used was 60% solution B and 40% solution A for 11 min. The flow rate was 0.5 mL s⁻¹. The injection amount was 1 μl . Calibration curves of standard chemicals were employed to



determine and quantify the products. The total conversion and selectivities were calculated using the following equations:

$$\text{Conv. \%} = \frac{\text{moles of BZH consumed}}{\text{initial moles of BZH}} \times 100\% \quad (1)$$

$$\text{Sel}_{\text{BA}} \% = \frac{\text{ratio of BA}}{\text{conversion ratio amount of BZH}} \times 100\% \quad (2)$$

$$\text{Sel}_{\text{HDB}} \% = \frac{2 \times \text{ratio of HDB}}{\text{conversion ratio amount of BZH}} \times 100\% \quad (3)$$

2.6 Electrocatalytic tests.

The electrochemical performance of the electrocatalyst was evaluated on a Corrtest CS2350 EIS bipotentiostat (2-channel, Wuhan Corrtest Instrument Corp. Ltd) using a 3-electrode system in an H-cell reactor divided by a Nafion 117 proton exchange membrane. The working electrode was prepared as follows: 9 mg powder was dispersed into 500 μL H_2O , 420 μL methanol, and 80 μL 5% Nafion solution. For activity, conversion, and selectivity determination, the catalyst was supported on a carbon cloth used as working electrodes. 1000 μL ink solution was dropped on $2 \times 3 \text{ cm}^2$ carbon cloth ($\sim 1.5 \text{ mg cm}^{-2}$) that was then cut into $1.5 \times 1 \text{ cm}^2$ pieces. When testing, an electrode area of $1 \times 1 \text{ cm}^2$ was immersed into the solution. To determine activation energies, 6 μL ink solution was dropped on a glassy carbon working electrode ($d=0.15 \text{ cm}$, $\sim 0.7 \text{ mg cm}^{-2}$) and let dry. Platinum mesh and Ag/AgCl (KCl saturated) were used as counter and reference electrodes, respectively. Cyclic voltammetry (CV) and linear sweep voltammetry (LSV) results were calibrated with Nernst equation (4) to the reference hydrogen electrode (RHE) without iR correction. The temperature effects were neglected when setting the parameters for I-t curves.

$$E_{\text{RHE}} = E + 0.0591 * \text{pH} + E_{\text{Ag/AgCl}}^{\theta} \quad (4)$$

where T represents temperature in $^{\circ}\text{C}$, and

$$E_{\text{Ag/AgCl(KCl saturated)}}^{\theta} = [0.197 - 0.0007 (T - 25)] \text{ V} \quad (5)$$

Two electrolytes were tested to explore the influence of the pH. A sodium acetate-acetic acid solution ($\text{pH}=5.2$), and a potassium carbonate-potassium bicarbonate solution ($\text{pH}=9.0$). LSV was tested in the range $0.5 \text{ V} \sim -1.0 \text{ V}$ (vs. RHE). Electrochemical impedance spectroscopy (EIS) was tested at -0.7 V vs. RHE. For the I-t curve, -0.4 V , -0.8 V , -1.0 V (vs. RHE) was applied as a constant voltage.

Results and discussion

Cu_2S and $\text{Cu}_2\text{S-OAm}$ electrocatalysts were prepared at $200 \text{ }^{\circ}\text{C}$ using a one-pot synthetic reaction followed by post-treatment (see details in the Experimental section, Figure 1a). DDT was employed as the source of S and solvent and OAm was used as an additional solvent and surface ligand. After 1 h reaction at $200 \text{ }^{\circ}\text{C}$, $\text{Cu}_2\text{S-OAm}$ was obtained by centrifugation. Cu_2S was obtained by annealing the $\text{Cu}_2\text{S-OAm}$ powder at $400 \text{ }^{\circ}\text{C}$ under an Ar atmosphere.

Figure 1b shows the $\text{Cu}_2\text{S-OAm}$ NPs to have spherical geometry and an average size of $10 \pm 2 \text{ nm}$. HRTEM micrographs of $\text{Cu}_2\text{S-OAm}$

reveal their hexagonal crystal phase, space group $P6_3\text{mmC}$ with $a=b=3.95 \text{ \AA}$ and $c=6.75 \text{ \AA}$ (Figure 1c), which was consistent with XRD analysis results (PDF#00-02-1294, Figure 1d). HAADF intensity profiles and TEM-EDS chemical composition maps show a homogeneous dispersion of Cu and S within the $\text{Cu}_2\text{S-OAm}$ particles that are surrounded by a carbon-based shell (Figures 1e and S1). The carbon shell is discerned by the stronger carbon signal detected at the border of the particle and it is associated with the presence of OAm at the NP surface.

To remove OAm ligands from the NP surface, the material was annealed at $400 \text{ }^{\circ}\text{C}$ under an Ar atmosphere. The removal of the stabilizing ligands resulted in increased surface energy that, combined with the relatively high processing temperature, led to NP aggregation and additional growth into Cu_2S particles with irregular morphologies (Figure S2a). Yet, the hexagonal crystal phase of Cu_2S was maintained as shown by XRD characterization (Figure 1d). EDS analysis confirmed the Cu_2S composition to be close to the stoichiometric $\text{Cu:S} = 2:1$ (Figure S2e). Besides, HAADF intensity profiles and STEM-EDS elemental maps showed no evidence of an organic layer surrounding the Cu_2S particles, confirming the surface ligand removal (Figure S2). The complete ligand removal was further verified using FT-IR analysis (Figure 1f). The FT-IR spectrum of $\text{Cu}_2\text{S-OAm}$ displays the signal corresponding to the $-\text{NH}$ bending vibration at 1619 cm^{-1} and $-\text{NH}_2$ wagging vibration at 721 cm^{-1} , which indicates the presence of OAm molecules on the Cu_2S surface bond to the surface Cu by the amine polar groups to form OAm/Cu complex. Besides, the FT-IR spectrum of $\text{Cu}_2\text{S-OAm}$ does not show the band at 2577 cm^{-1} associated with the stretching vibration of S-H. This result indicates the lack of free alkylthiol and Cu thiolate complexes, i.e. the absence of DDT on the surface of the $\text{Cu}_2\text{S-OAm}$ NPs.^{35, 37} Peak signals at around 3000 cm^{-1} corresponds to the stretching vibration of both saturated and unsaturated C-H. On the other hand, the FT-IR spectrum of Cu_2S displayed no fingerprint associated with the presence of OAm or DDT, proving the successful ligand removal during the annealing process.



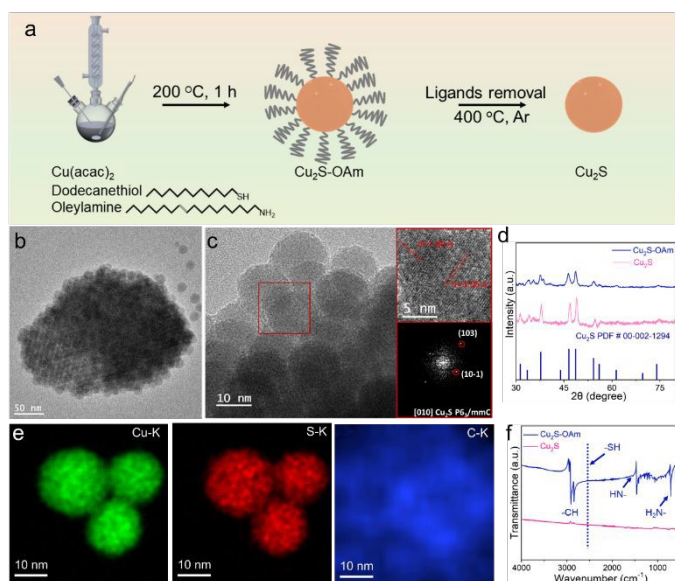


Figure 1. (a) Scheme of the procedure used to prepare $\text{Cu}_2\text{S-OAm}$ and Cu_2S . (b) TEM and (c) HRTEM images and indexed power spectrum of $\text{Cu}_2\text{S-OAm}$ NPs. From the crystalline domain, the Cu_2S lattice fringe distances were measured to be 0.1902 nm, 0.3057 nm, at 80.46° which is interpreted as the hexagonal Cu_2S phase, visualized along its [101] zone axis. (d) STEM-EDS chemical composition maps of $\text{Cu}_2\text{S-OAm}$ NPs; (e) XRD patterns of Cu_2S and $\text{Cu}_2\text{S-OAm}$. (f) FT-IR spectra of Cu_2S and $\text{Cu}_2\text{S-OAm}$.

The survey and high-resolution XPS spectra are displayed in Figures S3 and 2, respectively. The Cu 2p XPS spectrum of $\text{Cu}_2\text{S-OAm}$ displays a unique doublet, at 932.1 eV ($\text{Cu } 2p_{3/2}$), associated with Cu(I) within the Cu_2S lattice.³⁵ In contrast, the Cu 2p XPS spectrum of Cu_2S displays two doublets and additional satellite peaks. The first doublet, at 932.1 eV ($\text{Cu } 2p_{3/2}$), is associated with Cu(I) within the Cu_2S lattice. The second doublet, at 934.3 eV ($\text{Cu } 2p_{3/2}$), and the satellites are related to the presence of a significant amount of Cu(II) at the Cu_2S surface. This second component is associated with the oxidation of Cu(I) after ligand removal. The S 2p XPS spectrum of $\text{Cu}_2\text{S-OAm}$ shows one doublet at 161.5 eV ($\text{S } 2p_{3/2}$) which is assigned to S ions coordinated to Cu within the Cu_2S lattice. A second minor component is observed at lower binding energies, 160.9 eV ($\text{S } 2p_{3/2}$), which we associate with sulfur next to OAM-bond metal ions. After the ligand removal, the S 2p XPS spectrum of Cu_2S shows just one doublet associated with S ions within the Cu_2S lattice. This component is redshifted by around 0.4 eV, which indicates a higher electron concentration around the surface S within the Cu_2S sample.

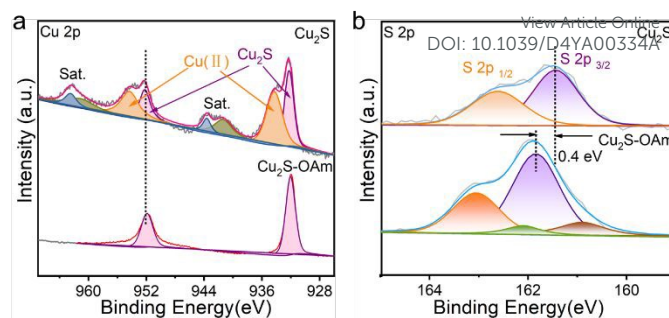


Figure 2. High-resolution Cu 2p (a) and S 2p (b) XPS spectra of Cu_2S and $\text{Cu}_2\text{S-OAm}$.

The electrochemical properties of Cu_2S and $\text{Cu}_2\text{S-OAm}$ particles supported on glassy carbon were initially tested in acidic conditions, within a 1M sodium acetate-acetic acid electrolyte (pH=5.2) with and without 20 mM BZH. Lower pH values were not considered as pH values below 5.2 might cause C=O cleavage of BZH to toluene or other side products. Figure 3a displays the LSV curves obtained in a three-electrodes H-cell reactor. In acidic conditions, without BZH, electrons are only transferred to H^+ to form H_{ad} , thus the measured current densities in the absence of BZH correspond to the HER. We observe that the $\text{Cu}_2\text{S-OAm}$ electrode displays a significantly lower HER activity, with a higher overpotential and lower current densities at all applied voltages than the Cu_2S electrode. This result is consistent with the presence of OAM partially inhibiting H_{ad} formation and HER. In the presence of BZH, electrons can be also transferred to C in $\text{ph-HC=O-H}_3\text{O}^+$ to form a ketyl radical. The subsequent step, after the electron transfer process, involves the combination of the ketyl radical and H_{ad} into BA or the combination of ketyl radicals into BZH, involving no additional charge transfer. For both electrodes, the addition of BZH in the electrolyte results in a current increase at low negative potentials, below the HER onset potential. This implies that ketyl radicals are readily formed at lower negative voltages than H_{ad} and H_2 , at ca. -0.3 V vs. RHE in both electrodes. For the $\text{Cu}_2\text{S-OAm}$ electrode, the current density in the presence of BZH is systematically higher than in its absence, at all potentials tested, which reflects a promoted ketyl radical generation over the partially inhibited H_{ad} formation and H_2 evolution. As for the Cu_2S electrode, while at low negative potentials, the current density is higher in the presence of BZH, as the applied potential increases, the HER-related current in the absence of BZH overcomes the combination of the current density associated with the BZH reaction and the HER in the presence of BZH. Thus the presence of BZH partially inhibits the HER in this material, potentially as a result of the ketyl radical reaction with H_{ad} , reducing its concentration, or through the adsorption of $\text{ph-HC=O-H}_3\text{O}^+$ or the ketyl radical on the Cu_2S surface thus occupying H_{ad} adsorption sites.

LSV curves depend on charge transfer frequency. They are influenced by mass transport in the electrode and solution, the intrinsic catalytic properties and the number of available adsorption and reaction sites. Thus processes that do not involve charge transfer but potentially blocking/releasing reaction sites such as the ketyl radical conversion to BA through reaction with a H_{ad} play also an important role. EIS spectra were used for a more precise characterization of the charge transfer mechanisms, without the involvement of site density and occupancy.



EIS spectra of the two electrodes at -0.7 V vs. RHE in the presence and absence of BZH show one semicircle associated with the impedance of the charge transfer from the electrode surface to the electrolyte species (R_{ct}). The R_{ct} of Cu_2S -OAm in the absence of BZH is significantly larger than that of Cu_2S , which is consistent with the inhibition of the H^+ adsorption and H_2 evolution being related not to a lower site density but to a larger barrier for electron transfer to H^+ in solution probably related to the long OAm chains. We observe the series resistance (R_s) to slightly decrease in the presence of BZH, which is related to an increase of the electrolyte conductivity in the presence of the generated $\text{ph-HC=O-H}_3\text{O}^+$ and ketyl radicals. Besides, both, Cu_2S and especially Cu_2S -OAm electrodes show much smaller R_{ct} values in the presence of BZH. This is consistent with LSV data for Cu_2S -OAm but it is in contrast with LSV data for Cu_2S . The smaller R_{ct} is associated with the easier electron transfer from the electrode to BZH and formation of ketyl radical than to H^+ to form H_{ad} . This result, combined with LSV data, shows the slower kinetics detected in the presence of BZH to be related to the BZH radical conversion to BA instead of the ketyl radical formation. The charge transfer resistance of Cu_2S -OAm in the presence of BZH is slightly smaller than that of Cu_2S , which is surprising taking into account the presence of OAm hindering charge transfer to species in solution. We associate these results with the hydrophobic surface of Cu_2S -OAm that leads to an enrichment of BZH, facilitating electron transfer to $\text{ph-HC=O-H}_3\text{O}^+$. Also, the possibility of partial electron transfer to OAm in Cu_2S -OAm cannot be ruled out.

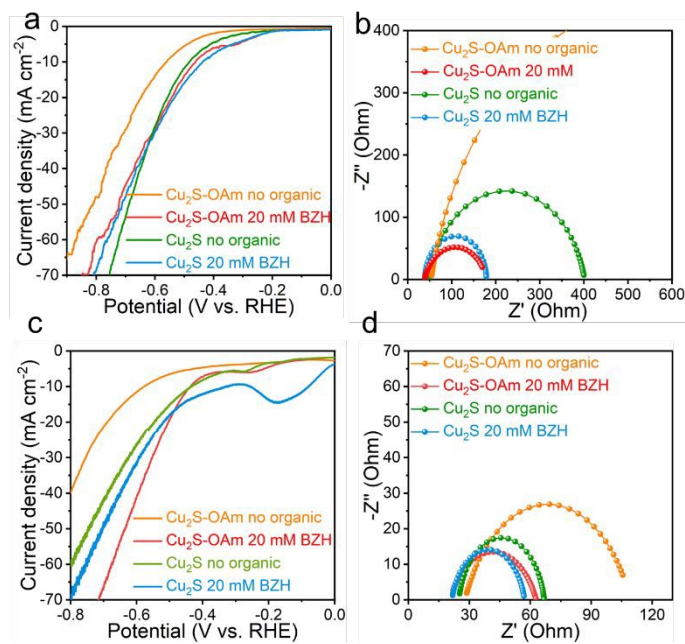


Figure 3. (a) LSV curves; (b) Nyquist plots at -0.7 V vs. RHE of Cu_2S -OAm and Cu_2S in 1M sodium acetate-acetic acid electrolyte ($\text{pH}=5.2$) with and without BZH at room temperature; (c) LSV curves; (d) Nyquist plot at -0.7 V vs. RHE of Cu_2S -OAm and Cu_2S in 1 M potassium carbonate-potassium bicarbonate electrolyte ($\text{pH}=9$) with or without BZH at room temperature.

In an acidic solution, under an applied voltage, the OAm of the Cu_2S -OAm surface may accept electrons and could be also replaced by H^+ .³⁸ Therefore, the stability of the Cu_2S and Cu_2S -OAm electrode in 1M sodium acetate-acetic acid electrolyte ($\text{pH}=5.2$) was further analyzed (Figure S4). The repetitive CV curves showed Cu_2S to have good stability both with and without BZH. In contrast, the current density obtained from the Cu_2S -OAm electrode was not constant. It increased in an electrolyte containing 20 mM BZH and decreased in the pure electrolyte. These results indicate that the OAm ligand undergoes slight reaction/substitution. Still, after more than 20 cycles, the effect of OAm on the Cu_2S -OAm electrode is clearly noticed (Figure S5).

Results obtained in alkaline conditions, using glassy carbon with 1M potassium carbonate-potassium bicarbonate electrolyte ($\text{pH}=9.0$), are displayed in Figure 3d-f. In these conditions, due to the significant suppression of HER, the concentration of ketyl radicals is expected to increase, resulting in an enhancement of their self-coupling. Indeed, in the absence of BZH, a clear decrease in the HER-related current densities is observed for both electrode materials. LSV curves show the current densities to significantly increase when adding BZH into the system for Cu_2S -OAm (Figure 3d), displaying a similar onset potential as in acidic conditions, but providing overall lower current densities at higher negative voltages due to the lower HER contribution. For Cu_2S , current densities show a much slighter variation in the presence of BZH, as in the acidic case.

EIS spectra of the two electrodes in basic conditions at -0.7 V vs. RHE are displayed in Figure 3f. A notable decrease of R_{ct} is noticed in alkaline conditions compared with acidic ones in the absence of BZH, associated with the enhancement of radical-radical coupling. At low pH, the hydrogen binding strength is lower due to the surrounding hydronium ions,³⁹ which facilitates the formation of H_{ad} that combines with the ketyl radicals to produce benzyl alcohol. As the pH increases, the formation of H_{ad} requires overcoming a higher energy barrier. Thus radicals are more inclined to undergo self-coupling, which further accelerates the charge transfer and radical formation. With the introduction of BZH, both electrodes display similar tendencies as in acidic conditions, with a notable decrease of the R_{ct} attributed to the formation of ketyl radicals.

As observed from the CV curves (Figure S6), the performance of the Cu_2S electrode was stable both with and without BZH (Figure S6a-b). In contrast, the current density increased for Cu_2S -OAm electrodes in the pure electrolyte, indicating moderate stability in these conditions, potentially due to ligand displacement with $-\text{OH}$.³⁸ This instability was not observed in the presence of BZH (Figure S7), which indicates a smooth and efficient transfer of charge to BZH.



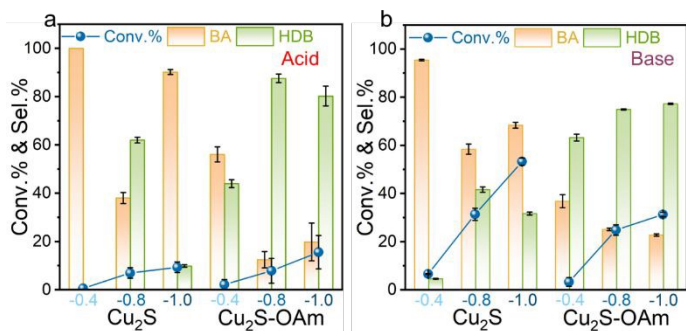


Figure 4. BZH conversion and selectivity toward BA and HDB after 20 min reaction on Cu₂S and Cu₂S-OAm electrodes at 0.4, -0.8, -1.0 V vs. RHE, 25 °C in (a) 1 M sodium acetate-acetic acid solution (pH=5.2) with 20 mM BZH; (b) 1 M potassium carbonate-potassium bicarbonate solution (pH=9.0) with 20 mM BZH.

To quantify the reaction products, additional electrocatalytic measurements were carried out with the materials supported on CC using a constant reaction time of 20 min. Different pH, voltage, and temperature conditions were tested to evaluate the effect of these parameters on the BZH conversion and product selectivity.

Figure 4 shows the effect of the applied potential on the BZH conversion and selectivity. Under acidic conditions (Figure 4a), at a low voltage of -0.4 V vs. RHE, both Cu₂S and Cu₂S-OAm catalysts exhibit relatively low BZH conversion (~5%), and notable selectivity towards BA, especially Cu₂S. This result is attributed to the hydrogen bonding to the catalyst surface, forming Cu-H bonds at low negative voltages. Then, this H is combined with ketyl radical.⁴⁰ As the negative voltage increases, the conversion increases. Additionally, as increasing the voltage, the selectivity of the two electrodes towards the conversion of BZH into BA first decreases and then increases again. The voltage increase elevates the electrochemical potential at the electrode-solution interface, augmenting the formation of H_{ad}, thereby bolstering BA selectivity. As expected, Cu₂S-OAm exhibited higher selectivity to HDB at all voltages due to the inhibited formation of H_{ad}. The slight decrease in HDB selectivity obtained for Cu₂S-OAm at high voltage may be related to the partial OAM reaction/replacement from the Cu₂S surface.

Under basic conditions (Figure 4b), a substantial increase in BZH conversion is measured, but the selectivity trends with the applied voltage remain unchanged. Notably, the selectivity of Cu₂S-OAm towards the conversion of BZH into HDB increases with the voltage, which is consistent with good catalyst stability.

The reactant concentration effect was also analyzed. The results are summarized in Table S1. It can be observed that the BZH conversion is slightly increased with higher reactant concentration within the same reaction time on different pH and the same electrode materials, while the selectivity towards BA or HDB shows no significant change on the same electrode materials.

A temperature increase also results in an elevation of the material surface Fermi level thus leading to a decrease of the charge transfer resistance and the formation of additional H_{ad}. Therefore, a similar dependence to that obtained for the voltage is expected. The difference lies in that the temperature also accelerates the mass transfer efficiency in the solution. At -0.8 V vs. RHE, the Cu₂S selectivity towards BA increased with temperature both in acid and

alkaline conditions owing to the higher H_{ad} formed. The Cu₂S selectivity towards BA is higher under acidic conditions compared to alkaline in the whole temperature range tested. For Cu₂S-OAm, the selectivity towards HDB decreased with temperature in acidic conditions, owing to the H_{ad} increase. However, the HDB selectivity increased with temperature under alkaline conditions.

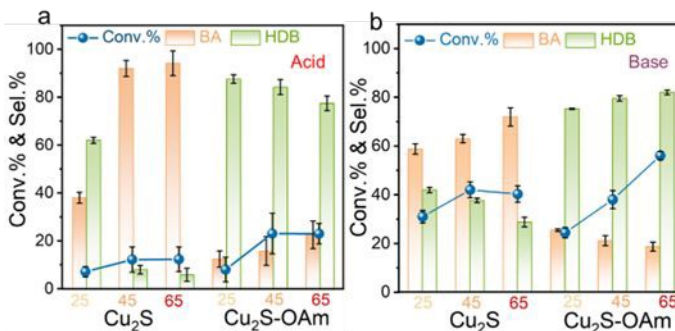


Figure 5. BZH conversion and selectivity toward BA and HDB after 20 min reaction on Cu₂S and Cu₂S-OAm electrodes at -0.8 vs. RHE, 25 °C, 45 °C or 65 °C in (a) 1 M sodium acetate-acetic acid solution (pH=5.2) with 20 mM BZH; (b) 1 M potassium carbonate-potassium bicarbonate solution (pH=9.0) with 20 mM BZH.

To further understand the effect of temperature on mass transfer and the acceleration of the reaction rate, EIS measurements at different temperatures were carried out on the catalysts supported on glassy carbon. From these results, the corresponding activation energy barriers were calculated (Figures 6 and S8). As pH increased, the reaction energy barrier in Cu₂S decreased from 70 kJ/mol to 44 kJ/mol. In contrast, the energy barrier in Cu₂S-OAm increased from 46 kJ/mol to 61 kJ/mol. These results imply the higher sterical barriers for the formation of H_{ad} to combine with the hydroxyl carbon of the intermediate ketyl radical in alkaline than in acidic conditions, while BZH can combine with H⁺ in acidic conditions to form ketyl radical more easily than in alkaline.

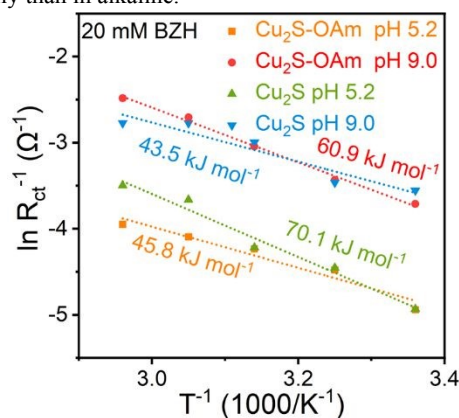


Figure 6. Activation energies calculated from the Nyquist plot.

Based on the above results, it is clear that a high selectivity for obtaining HDB by BZH electrochemical reduction can be achieved by adjusting the pH, applied voltages, catalyst components and catalyst surface properties. The energy barrier for the formation of the high-energy intermediate species H_{ad} increases as the pH increases, leading to a decrease in the concentration of H_{ad} on the catalyst surface, thereby increasing the chances of radical dimerization for the formation of HDB. For catalysts with exposed active sites, applying a



higher voltage leads to surface electron accumulation, causing enrichment of H⁺ on the EDL solution side, and increasing the possibility of forming H_{ad} and BA. Thus, blocking the active sites of the catalyst surface with organic ligands to prevent the formation of H_{ad} can improve the selectivity of HDB independently of pH.

Conclusions

In summary, Cu₂S-OAm and Cu₂S were synthesized using a one-pot synthetic approach and a post-treatment process. By comparing their electrocatalytic performance in the electrochemical reduction of BZH, we conclude that OAm prevents the organic substrate and the H proton from reaching the Cu₂S active sites. Consequently, hydrogen cannot become activated to combine with ketyl radicals to form BA. At the same time, the organic BZH and its ketyl radicals concentrate near the OAm ligands on the catalyst surface due to their similar polarity, thus promoting selectivity and conversion towards forming HDB.

Author contributions

Li Gong: Conceptualization and Writing – original draft; Shiling Zhao and Tanja Kallio: Investigation; Jing Yu, Jordi Arbiol and Junshan Li: Formal Analysis; Paulina R. Martínez-Alanis: Supervision and Funding acquisition; Mariano Calcabrini and Maria Ibáñez: Methodology; Andreu Cabot: Supervision and Writing – review & editing.

Conflicts of interest

There are no conflicts to declare.

Data availability

No data were used for the research described in this article.

Acknowledgements

L. Gong and J. Yu thank the China Scholarship Council for the scholarship support. ICN2 acknowledges funding from Generalitat de Catalunya 2021SGR00457. This study is part of the Advanced Materials programme and was supported by MCIN with funding from European Union NextGenerationEU (PRTR-C17.11) and by Generalitat de Catalunya. The authors thank support from the project NANOGEN (PID2020-116093RB-C43), funded by MCIN/AEI/10.13039/501100011033/ and by “ERDF A way of making Europe”, by the “European Union”. ICN2 is supported by the Severo Ochoa program from Spanish MCIN / AEI (Grant No.: CEX2021-001214-S) and is funded by the CERCA Programme / Generalitat de Catalunya. Part of the present work has been performed in the framework of Universitat Autònoma de Barcelona Materials Science PhD program. Authors acknowledge the use of instrumentation as well as the technical advice provided by the Joint Electron Microscopy Center at ALBA (JEMCA). ICN2 acknowledges funding from Grant IU16-014206 (METCAM-FIB) funded by the European Union through the European Regional Development Fund (ERDF),

with the support of the Ministry of Research and Universities, Generalitat de Catalunya. ICN2 is founding member of DREAM41

Notes and references

- G. Zeng, Q. Sun, S. Horta, S. Wang, X. Lu, C. Y. Zhang, J. Li, J. Li, L. Ci, Y. Tian, M. Ibáñez and A. Cabot, *Adv. Mater.*, 2024, **36**, 2305128.
- C. Huang, J. Yu, C. Li, Z. Cui, C. Zhang, C. Zhang, B. Nan, J. Li, J. Arbiol and A. Cabot, *Adv. Funct. Mater.*, 2023, **33**, 2305624.
- U. Sanyal, K. Koh, L. C. Meyer, A. Karkamkar and O. Y. Gutiérrez, *J. Appl. Electrochem.*, 2021, **51**, 27-36.
- Y. P. Wijaya, K. J. Smith, C. S. Kim and E. L. Gyenge, *Green Chem.*, 2020, **22**, 7233-7264.
- S. A. Akhade, N. Singh, O. Y. Gutiérrez, J. Lopez-Ruiz, H. Wang, J. D. Holladay, Y. Liu, A. Karkamkar, R. S. Weber, A. B. Padmaperuma, M.-S. Lee, G. A. Whyatt, M. Elliott, J. E. Holladay, J. L. Male, J. A. Lercher, R. Rousseau and V.-A. Glezakou, *Chem. Rev.*, 2020, **120**, 11370-11419.
- K. Li and Y. Sun, *Chem. - Eur. J.*, 2018, **24**, 18258-18270.
- J. Li, L. Li, X. Ma, X. Han, C. Xing, X. Qi, R. He, J. Arbiol, H. Pan, J. Zhao, J. Deng, Y. Zhang, Y. Yang and A. Cabot, *Adv. Sci.*, 2023, **10**, 2300841.
- J. Li, X. Tian, X. Wang, T. Zhang, M. C. Spadaro, J. Arbiol, L. Li, Y. Zuo and A. Cabot, *Inorg. Chem.*, 2022, **61**, 13433-13441.
- Z. Zhang, L. Bian, H. Tian, Y. Liu, Y. Bando, Y. Yamauchi and Z.-L. Wang, *Small*, 2022, **18**, 2107450.
- M. Luo, J. Yang, X. Li, M. Eguchi, Y. Yamauchi and Z.-L. Wang, *Chem. Sci.*, 2023, **14**, 3400-3414.
- J. Li, L. Li, X. Ma, J. Wang, J. Zhao, Y. Zhang, R. He, Y. Yang, A. Cabot and Y. Zhu, *Nano Res.*, 2023, DOI: 10.1007/s12274-023-6049-4.
- J. Li, L. Li, X. Ma, X. Han, C. Xing, X. Qi, R. He, J. Arbiol, H. Pan, J. Zhao, J. Deng, Y. Zhang, Y. Yang and A. Cabot, *Adv. Sci.*, 2023, **10**, 2300841.
- Z. J. Schiffer and K. Manthiram, *Joule*, 2017, **1**, 10-14.
- J. T. Bhanushali, I. Kainthla, R. S. Keri and B. M. Nagaraja, *ChemistrySelect*, 2016, **1**, 3839-3853.
- D. C. Cantu, A. B. Padmaperuma, M.-T. Nguyen, S. A. Akhade, Y. Yoon, Y.-G. Wang, M.-S. Lee, V.-A. Glezakou, R. Rousseau and M. A. Lilga, *ACS Catal.*, 2018, **8**, 7645-7658.
- C. Xu, E. Paone, D. Rodríguez-Padrón, R. Luque and F. Mauriello, *Chem. Soc. Rev.*, 2020, **49**, 4273-4306.
- M. T. Bender, X. Yuan, M. K. Goetz and K.-S. Choi, *ACS Catal.*, 2022, **12**, 12349-12368.
- J. Yu, P. Zhang, L. Li, K. Li, G. Zhang, J. Liu, T. Wang, Z.-J. Zhao and J. Gong, *Nat. Commun.*, 2022, **13**, 7909.
- S. Huang, B. Gong, Y. Jin, P. H. L. Sit and J. C.-H. Lam, *ACS Catal.*, 2022, **12**, 11340-11354.
- L. C. Meyer, U. Sanyal, K. A. Stoerzinger, K. Koh, J. L. Fulton, D. M. Camaioni, O. Y. Gutiérrez and J. A. Lercher, *ACS Catal.*, 2022, **12**, 11910-11917.
- X. H. Chadderdon, D. J. Chadderdon, J. E. Matthiesen, Y. Qiu, J. M. Carraher, J.-P. Tessonnier and W. Li, *J. Am. Chem. Soc.*, 2017, **139**, 14120-14128.
- H. Liu, D. M. Patel, Y. Chen, J. Lee, T.-H. Lee, S. D. Cady, E. W. Cochran, L. T. Roling and W. Li, *ACS Catal.*, 2022, **12**, 14072-14085.
- J. Anibal and B. Xu, *ACS Catal.*, 2020, **10**, 11643-11653.
- P. Nilges and U. Schröder, *Energy Environ. Sci.*, 2013, **6**, 2925-2931.



25. T. Guena and D. J. A. C. S. Pletcher, 1998, **52**, 23-31.
26. X. H. Chadderdon, D. J. Chadderdon, J. E. Matthiesen, Y. Qiu, J. M. Carraher, J. P. Tessonnier and W. Li, *J Am Chem Soc*, 2017, **139**, 14120-14128.
27. J. Anibal, A. Malkani and B. Xu, *Catal. Sci. Technol.*, 2020, **10**, 3181-3194.
28. L. Gong, C. Y. Zhang, J. Li, G. Montaña-Mora, M. Botifoll, T. Guo, J. Arbiol, J. Y. Zhou, T. Kallio, P. R. Martínez-Alanis and A. Cabot, *ACS Appl. Mater. Interfaces.*, 2024, **16**, 6948-6957.
29. L. Gong, C. Y. Zhang, X. Mu, X. Han, J. Li, J. Arbiol, J. Y. Zhou, T. Kallio, P. R. Martínez-Alanis and A. Cabot, *J. Chem. Eng.*, 2024, **479**, 147612.
30. J. Wu, D. Liang, X. Song, T. Liu, T. Xu, S. Wang and Y. Zou, *J. Energy Chem.*, 2022, **71**, 411-417.
31. K. Koh, U. Sanyal, M.-S. Lee, G. Cheng, M. Song, V.-A. Glezakou, Y. Liu, D. Li, R. Rousseau, O. Y. Gutierrez, A. Karkamkar, M. Derewinski and J. A. Lercher, *Angew. Chem.*, 2020, **59**, 1501-1505.
32. F. Wang and S. S. Stahl, *Acc. Chem. Res.*, 2020, **53**, 561-574.
33. R. Cheng, Y. Min, H. Li and C. Fu, *Nano Energy*, 2023, **115**, 108718.
34. J. Heo, H. Ahn, J. Won, J. G. Son, H. K. Shon, T. G. Lee, S. W. Han and M.-H. Baik, *Science*, 2020, **370**, 214-219.
35. A. Tang, S. Qu, K. Li, Y. Hou, F. Teng, J. Cao, Y. Wang and Z. Wang, *Nanotechnol.*, 2010, **21**, 285602.
36. Y. Zhang, C. Xing, Y. Liu, M. C. Spadaro, X. Wang, M. Li, K. Xiao, T. Zhang, P. Guardia, K. H. Lim, A. O. Moghaddam, J. Llorca, J. Arbiol, M. Ibáñez and A. Cabot, *Nano Energy*, 2021, **85**.
37. A. Shavel, M. Ibáñez, Z. Luo, J. De Roo, A. Carrete, M. Dimitrievska, A. Genç, M. Meyns, A. Pérez-Rodríguez, M. V. Kovalenko, J. Arbiol and A. Cabot, *Chem. Mater.*, 2016, **28**, 720-726.
38. L. Lu, B. Lou, S. Zou, H. Kobayashi, J. Liu, L. Xiao and J. Fan, *ACS Catal.*, 2018, **8**, 8484-8492.
39. I. K. M. Yu, F. Deng, X. Chen, G. Cheng, Y. Liu, W. Zhang and J. A. Lercher, *Nat. Commun.*, 2022, **13**, 7154.
40. B. M. Tackett, D. Raciti, A. R. Hight Walker and T. P. Moffat, *J. Phys. Chem. Lett.*, 2021, **12**, 10936-10941.
41. R. Ciancio, R. E. Dunin-Borkowski, E. Snoeck, M. Kociak, R. Holmestad, J. Verbeeck, A. I. Kirkland, G. Kothleitner and J. Arbiol, *Microscopy and Microanalysis*, 2022, **28**, 2900-2902.

View Article Online
DOI: 10.1039/D4YA00334A

Open Access Article. Published on 12 July 2024. Downloaded on 17/07/2024 18:25:24.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.



Data for this article, including original data are available at onedrive at https://irecedu-my.sharepoint.com/personal/gongli_irec_cat/_layouts/15/onedrive.aspx?view=0&id=%2Fpersonal%2Fgongli%5Firec%5Fcat%2FDocuments%2FE4%B8%BA%E4%BA%86%E6%AF%95%E4%B8%9A%2FA3

View Article Online
DOI: 10.1039/D4YA00334A

Open Access Article. Published on 12 July 2024. Downloaded on 17/07/2024 18:25:24.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.

