RSC Advances



PAPER

View Article Online
View Journal | View Issue



Cite this: RSC Adv., 2024, 14, 12475

Gamma-irradiated stibnite thin films set a remarkable benchmark performance for photoelectrochemical water splitting

Adel Chihi *

The study sets out to show the positive impact of sulfur vacancy engineering on the structural, morphological, optical, electrical, and photoelectrochemical (PEC) properties of Sb₂S₃ films synthesized using the spin coating technique. The produced films were exposed to γ -irradiation with different doses from 0 to 20 kGy. We have demonstrated the formation of sulfur vacancies and loss of oxygen content in the irradiated samples. XRD measurements revealed that all films exhibit a polycrystalline structure, and the crystallite size increases with the rising radiation dose, reaching the highest value of 87.4 nm measured for the Sb₂S₃ film irradiated with 15 kGy. The surface roughness of the irradiated samples increases with increasing γ -irradiation dose. The increase in surface roughness not only raises the active sites but enhances the conductivity of the Sb_2S_3 material as well. The wettability properties of the irradiated films were affected by γ -irradiation doses and the sample irradiated with 15 kGy exhibited the lowest hydrophobicity compared to others. The Hall measurements reveal that irradiated samples exhibit p-type semiconductor behavior. The optical band gap decreased progressively from 1.78 eV to 1.60 eV up to the irradiation dose of 15 kGy and slightly increased thereafter. The irradiated sample with 15 kGy showed a maximum photocurrent density of ca. 1.62 mA cm⁻² at 0 V vs. reverse hydrogen electrode (RHE) under AM 1.5 G illumination with applied bias photon-to-current efficiency (ABPE) of 0.82% at 0.47 V vs. RHE, suggesting superior PEC water splitting performance compared to other samples. At 0 V vs. RHE and 648 nm, the incident photon current efficiency (IPCE) and absorbed photon current efficiency (APCE) of the photocathode irradiated with 15 kGy are significantly higher than those of the other photocathodes with values of 9.35% and 14.47%, respectively. Finally, Mott-Schottky measurement was also performed on all photocathodes to estimate their acceptor density and flat band potential.

Received 22nd February 2024 Accepted 11th April 2024

DOI: 10.1039/d4ra01382d

rsc.li/rsc-advances

1. Introduction

Growing global affluence and population are driving the current surge in interest in renewable energy technology, as the world's energy consumption is predicted to reach over 240 million barrels per day by 2035, combined with depleting fossil fuel sources.¹ The production of dihydrogen (H₂) through solar water splitting, referred to as solar-to-hydrogen (STH), serves as the ultimate source of all the energy consumed today. This process provides a sustainable and environmentally friendly energy solution for future generations,²,²,³ playing a crucial role in propelling the transition toward a global carbon-neutral social economy and positioning it as a key facilitator for a greener and more sustainable future.⁴ In this regard, creating clean hydrogen using solar energy has garnered international attention as it presents a viable solution for alleviating the escalating energy costs in developed countries.⁵ To fulfill the

Photovoltaic Laboratory, Research and Technology Centre of Energy, Borj-Cedria Science, and Technology Park, BP 95, 2050 Hammam Lif, Tunisia. E-mail: supereagle2791@yahoo.fr

sustainable energy purpose, photoelectrochemical (PEC) water splitting is amongst the most promising technologies for STH production to develop renewable energy. 6,7 Some challenges associated with water-splitting cells include high energy consumption, deterioration of electrodes over time, and the need for catalysts to facilitate the chemical reaction ($2H_2O \rightarrow$ 2H₂ + O₂). Research is currently underway to address these challenges and improve the efficiency and durability of electrolysis technologies. Among the available solutions, the PEC system stands out as an economically feasible water-splitting cell. It is constructed using cost-effective semiconductor materials, making it a practical choice for this purpose.8 Presently, the most reported low-cost photoelectrodes are composed of semiconductors, such as $CuIn_xGa_{(1-x)} Se_2$, $CuBi_2O_4$ (ref. 10), and Cu₂O. 11 Among the semiconductors, antimony sulfide Sb₂S₃ would be a respectable candidate for use in PEC water splitting12 thanks to its economic cost, lacks chemical elements with limited availability or elevated levels of toxicity, including Indium (In), Tellurium (Te), Cadmium (Cd), and Lead (Pb). It also exhibits strong optical absorption ($\alpha > 10^4 \text{ cm}^{-1}$) in the visible range and near-IR spectral range,13 a direct band gap of

1.5-1.7 eV,14,15 has one-dimension (1D) parallel nano-ribbon grain structure (Sb₄S₆)_n, ^{16,17} power conversion efficiency about 7.5%.18 In contrast to other semiconductor materials like Si, CdTe, and $CuIn_xGa_{(1-x)}Se_2$ (CIGS), Sb_2S_3 possesses intrinsically advantageous properties at grain boundaries (GBs). Indeed, they can impede the motion of dislocations, act as barriers to charge carriers, facilitate charge transfer processes, and improve thermal conductivity. These characteristics make GBs crucial in determining the overall properties and performance of Sb₂S₃ materials. This inherent quality provides a promising and sustainable solution to the challenges associated with conventional semiconductor absorber materials. In those conventional materials, the disruption of covalent bonds leads to the emergence of defect states and recombination centers along GBs, posing a substantial barrier to charge collection and potentially reducing device efficiency owing to recombination at interfaces. Nevertheless, the Sb₂S₃ semiconductor has drawbacks such as electron-hole recombination, native defects (interstitial sulfur (Si), vacancies of Sb, and antisite substitutions (S_{Sb}, Sb_s), 19 what is more, the slow charge transfer kinetics limits the PEC performance and leads to reduced stability of the Sb₂S₃ material. In response to these enormous obstacles, scientists have put forward numerous strategies for achieving efficient and practical water splitting of Sb₂S₃ semiconductors. Numerous common technologies have been employed, including a protective layer,20 morphology control,21 doping technique,22 cocatalyst material,23 and so on. Consistent with previous studies, the introduction of surface defects through γ ray irradiation represents one of several approaches capable of modifying the structural, optical, and electrical properties of the target material.24 Indeed, the surface modification strategy produced by γ-radiation presents a straightforward and costeffective approach to enhancing PEC water splitting. This strategy offers several advantages, including its superior penetrating power compared to other techniques. Moreover, it can avoid contaminating the target material and generating radioactive by-products. In addition, γ ray irradiation could vary the band gap width (annihilate defect and/or create defects), accelerate the extraction rate of the photogenerated holes, rearrange the charge density, and generate more delocalized electrons, providing highly efficient and stable photoelectrodes for STH generation. So, γ -ray irradiation treatments can induce variations in material properties through a self-regulating process. This unique effect can be harnessed to design materials with desired properties. After γ-ray irradiation, various defects annihilated on the surface and in the bulk of Sb₂S₃ due to the cascade collision of irradiated ions and target material. These annihilated defects led to a rise in the electrical conductivity of Sb₂S₃ films, which ensured the rapid transport charge carriers and improved the PEC performance. The impact of γ-ray irradiation on the formation, structural, and optical properties of some semiconductor materials such as ZnO,25 TeO₂, ²⁶ ZnIn₂S₄, ²⁷ and g-C₃N₄ films²⁸ was also reported to boost the photocurrent density from 3.59 to 5.86 $\mu A \text{ cm}^{-2}$ at 1.23 V vs. $E_{Ag/AgCl}^0$, even though decreases the band gap energy from 2.82 to 2.76 eV. Han et al. found that the PEC water splitting of Sb₂Se₃ and Sb₂S₃.²⁹ Meanwhile, Wang et al. found that doping Sb₂S₃ film with the Bi element can control the phase composition and lattice parameters, resulting in a decrease in the optical band gap, a raise in the carrier concentration, and a decrease in the charge transfer resistance, which helps to improve the PEC performance.30 Numerous methods have been used to synthesize high-performance Sb₂S₃ photoelectrodes, including hydrothermal methods,31 chemical bath deposition,32 thermal evaporation methods,33 and so on. Among the various techniques, the spin coating process stands out for its efficiency and minimal material waste. It is considered an environmentally friendly thin film deposition technique in several industries. To the best of our knowledge, the experimental study of the influence of γ radiation on Sb₂S₃ films to improve the PEC water-splitting device has never been carried out. In this work, we investigate the effect of irradiation with γ-ray on the Sb₂S₃ semiconductor as an absorber layer grown on an ITO substrate by a fast-turnaround spin coating technique for efficient PEC water splitting. Compared to the morphology of a bare Sb₂S₃ thin film, the irradiated films displayed improved surface S vacancies and increased surfaceactive sites. This improvement helps to attenuate exciton pair recombination arising from deep-level defects in Sb₂S₃ material. By optimizing the γ-ray irradiation dose, the Sb₂S₃ photoelectrode with better performance was obtained. Besides, the PEC performance after irradiation with γ -ray increases, and the photocurrent density could reach 1.62 mA cm⁻² at 0 V vs. reverse hydrogen electrode (RHE), which is almost 2.7 times higher than the bare one. The improved photoelectrochemical (PEC) performance of irradiated Sb₂S₃ films is likely the result of a synergistic effect between increased light absorption and increased concentration of photogenerated carriers.

2. Experimental section

2.1 Chemicals

Antimony(III) chloride (SbCl₃, 97%), thiourea (CH₄N₂S, 99% pure), 2-methoxy ethanol (C₃H₈O₂, 98%), ethanol (C₂H₆O), acetone (C₃H₆O), and hydrochloric acid (HCl) were provided by Sigma-Aldrich company and employed as received without further treatment. The chemical reagents used for the synthesis were of analytical grade. Indium-doped tin oxide (ITO) conductive glass slides with surface resistivity of 10 Ω sq⁻¹ and thickness of 2.2 mm were used as substrates for the deposition of Sb₂S₃ thin films.

2.2 Synthesis of Sb₂S₃ photoelectrodes

The solution bath was made up of 1.5 mmol of antimony(III) chloride and 4 mmol of thiourea as antimony, and sulfur precursors, respectively. Each precursor was dissolved into 10 mL of 2-methoxy ethanol as solvent. After adjusting the pH of the acid bath with a carefully measured drop of HCl, the solution achieved the desired acidic conditions with a pH value of 4.³⁴ Afterward, the obtained solution was stirred uniformly under a constant magnetic field followed by heating to 60 °C for 30 min to produce a brown and homogeneous solution. The as-prepared

Sb₂S₃/Sb₂Se₃ heterojunction is three times higher than that of

Paper RSC Advances

solution was aged for about 10 hours. Before processing, the ITO substrates were thoroughly cleaned in acetone, ethanol, and deionized water of resistivity 18 MG for about 30 min inside an ultrasonic bath, and then dried under a stream of nitrogen. After that, the resulting solution was coated onto ITO-coated glass substrates at a fixed speed of 1000 rpm for 1 min with a spin coater at ambient temperature, as shown in Fig. 1. Subsequently, all samples were thermally treated on a hot plate in a protective atmosphere such as inert gas or reducing gas at an optimized temperature of 100 °C for 5 min to remove any undesirable organic compound. Lastly, the coating procedure cycle was done 5 times to realize the required thickness. The thickness of the spin-coated films ranges between 100 and 120 nm measured using a Bruker Dektak XT contact profilometer.

2.3 Characterization measurements

The binding energies (BE) of all the elements were performed using an ESCALAB 250 X-ray photoelectron spectrometer (XPS, Thermo Fisher Scientific). All the BE were calibrated to the C 1s peak of adventitious surface carbon at 284.8 eV. All chemical states of each element were determined according to the BE referenced in the National Institute of Standards and Technology (NIST) X-ray photoelectron spectroscopy database (NIST SRD 20) v. 5.0.35 The amount of Sb and S elements in all samples was measured by Inductively coupled plasma atomic emission spectroscopy (ICP-AES). Powder X-ray patterns were recorded on an automated Bruker D8 advance X-ray diffraction with a monochromatic CuK_{α} radiation source ($\lambda = 1.5406 \text{ Å}$) in the angle range from 20° to 60°. The Xpert high-score software was employed for phase identification and structure refinement. Raman scattering spectroscopy was conducted on all synthesized samples using a Jobin Yvon LabRAM HR spectrometer with a He-Ne laser source (632.81 nm). The surface morphology was examined by using atomic force microscopy (AFM) (a Nanoscope 3100 Digital instrument in tapping mode). The grain size and root mean square (RMS) surface roughness were determined by using Gwyddion software version 2.43 developed by Czech Metrology.36 Hall effect measurement was conducted in Van der Pauw configuration with a constant magnetic field of 0.5 T to reveal the electrical properties (resistivity (ρ), carrier concentration (N_e), and Hall mobility (μ_{Hall})) of obtained Sb₂S₃ thin films by using HMS5000 instrument. Optical transmission measurements were conducted by using NIR-UV-vis PerkinElmer Lambda 950 spectrophotometer equipped with an integrating sphere for light incidence in the wavelength range between 600 and 1200 nm at room temperature.



Fig. 1 Synthesis protocol for Sb₂S₃ thin films.

Photoluminescence (PL) measurements were performed by using an Ar+ ion laser lamp emitting a wavelength of 266 nm at room temperature. The spectra were detected through a 250 mm Jobin-Yvon monochromator and a GaAs photomultiplier in conjunction with a standard lock-in technique. The surface wettability of Sb₂S₃ thin films was assessed through water drop contact angle (CA) measurements using the DSA100 drop shape analyzer system from the Kruss Easy Drop goniometer. Water drops with a volume of 10 µl were dispersed over the surface using a micro-syringe. Then, the CAs were obtained via the tangent technique using the DSA3 software incorporated with the device. Finally, the γ -irradiation was performed at the National Center for Nuclear Sciences and Technologies of Tunis with an industrial 60Co radioactive source with an irradiated dose of 0.25 kGy h⁻¹. The obtained films were irradiated with γ irradiation at different doses ranging from 5 to 20 kGy.

2.4 Photoelectrochemical characterizations

The photocurrent was measured in a three-electrode system in the dark and under illumination on the synthesized samples with Sb₂S₃ thin films as the working electrode, saturated calomel as the reference electrode (SCE), and a Pt plate as the counter electrode. The data was achieved through a potentiostat/galvanostat Auto lab (model PGP201). These electrodes were vertically immersed in a 10 mL volume quartz cell, which contains Na_2SO_4 (0.5 M, pH \cong 7) a buffer electrolyte solution, as shown in Fig. 2. Before the PEC measurements, the solution bath was degassed by bubbling with N2 gas for at least 10 min before commencing the experiment, and N2 was continuously bubbled through the solution using Sierra's flagship SmartTrak 100 thermal mass flow controller (flow rate = 5 mL min^{-1}) throughout the measurement. Next, we apply a linear sweep voltammetry (LSV) mode with an anodic scan direction at the scan rate of 10 mV s⁻¹ under chopped white illumination by a light-emitting diode (LED), which has been switched on and off with an asymmetric duty cycle. To enhance precision and reduce error estimation, our measurements were conducted five times under the same conditions. Mott-Schottky (M-S) measurements were carried out at an AC frequency of 1 kHz and an amplitude of 10 mV in dark conditions. All the measured potentials were converted to RHE scale using Nernst's equation:




Fig. 2 Illustration for the three-electrode setup used in the photo-electrochemical technique. WE = working electrode (Sb₂S₃ thin films); RE = reference electrode (SCE); CE = counter electrode (Pt plate).

$$E (V vs. RHE) = E (V vs. SCE) + 0.059 pH + 0.244$$
 (1)

Incident photon-to-electron conversion efficiency (IPCE) and absorbed photon-to-current efficiency (APCE) measurements were collected at 0 V vs. RHE using a solar simulator coupled with a filter and an aligned monochromator in the same experimental setup as described above. IPCE and APCE values are determined using the following equation:

IPCE(%) =
$$\frac{1240 \times [j_{\text{light}} - j_{\text{dark}}]}{\lambda \times P_{\text{inc}}} \times 100$$
 (2)

$$APCE(\%) = \frac{IPCE(\lambda)}{1 - 10^{-A(\lambda)}}$$
(3)

where $j_{\rm light}$ is the steady-state photocurrent density, $j_{\rm dark}$ is the dark current density (mA cm⁻²), $P_{\rm inc}$ is the incident optical power density of monochromatic light (mW cm⁻²), λ is the monochromatic wavelength of light (nm), and $A(\lambda)$ is the optical absorption of the entire photoelectrode.

Applied bias photon-to-current efficiency (ABPE) for the PEC cell was calculated using the following relationship:

$$APBE(\%) = \frac{j \times \left[V_{H+/H_2} - V_b \right]}{P_{light}} \times 100$$
 (4)

where $V_{\rm b}$ denotes applied bias voltage vs. RHE, $V_{\rm H^+/H_2}$ is the thermodynamic potential for hydrogen evolution, and J is the measured photocurrent current density (mA cm $^{-2}$) taken after 30 s illumination at each $V_{\rm b}$. $P_{\rm light}$ is the incident light power density (100 mW cm $^{-2}$).

Results and discussion

3.1 XPS and ICP-AES analysis

XPS analysis was performed to assess whether any alterations in the elemental composition and chemical states of Sb_2S_3 thin films occurred following γ -ray irradiations. Fig. 3 shows the XPS survey spectrum of the bare Sb_2S_3 film, covering a BE range from

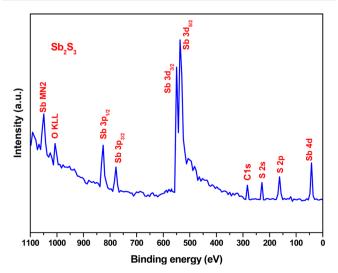


Fig. 3 High-resolution XPS spectra of bare Sb₂S₃ film.

0 to 1100 eV. The BE photoelectron lines of all XPS spectra are consistent with previous research studies.²² The photoelectron lines of oxygen and carbon elements are likely attributed to the formation of reactive oxide species and surface impurities, which are common in chalcogenide films when they encounter atmospheric air.³⁷ The presence of S²⁻ ions in the bare Sb₂S₃ material is indicated by the photoelectron lines for S at approximately 161.4 eV and 162.3 eV, which are assigned to the doublet S 2p_{3/2} and S 2p_{1/2}, respectively,³⁸ as shown in Fig. 4a. The corresponding spin-orbit splitting of S 2p is about 0.9 eV, while the intensity ratio of the two photoelectron lines in the doublet is S $2p_{3/2}$: S $2p_{1/2} = 2:1$. On the other hand, Sb photoelectron lines showed BE of 529.8 eV and 539.0 eV approving the presence of Sb 3d_{5/2} and Sb 3d_{3/2} states, respectively. The matching spin-orbit splitting of the Sb 3d photoelectron line is about 9.2 eV, while the two relative line intensities in the doublet are Sb $3pd_{5/2}$: Sb $3p_{3/2}$ = 3:2, which suggests the existence of Sb³⁺ valence states,³⁹ as shown in Fig. 4b. No satellite photoelectron lines were detected indicating that Sb is present only as Sb3+ ions. Considering the neutrality of the material, the XPS results suggest that the valence states for our synthesized Sb₂S₃ material are Sb₂³⁺S₃²⁻. To further investigate the influence of γ -ray irradiations on the chemical states of Sb₂S₃ thin films, the XPS spectrum of S and Sb with different irradiation doses is revealed in Fig. 5. It is widely recognized that XPS is primarily sensitive to the surface composition of the film, typically examining only the top 10 nm.40 Thus, we anticipate that there will be no significant variation in the chemical composition of the Sb₂S₃ film throughout its thickness after γ-ray irradiation. The spectral shape of both S and Sb core level spectra in bare and irradiated samples is nearly identical. This implies that in the irradiated Sb₂S₃ samples, the radiation dose does not promote the creation of an additional phase. It is interesting to note that the irradiated Sb_2S_3 samples showed an upward shift to the left (i.e., higher BE) of the S 2p core level photoelectron lines by about 0.18 eV compared to bare Sb₂S₃, indicating a slight change in the chemical environment of the sulfur atoms, as shown in Fig. 5a. However, the photoelectron line separation remained unaffected at 0.9 eV, meaning that the valence state of the S ion was still S^{2-} . Conversely, the signal intensity of S sites in the irradiated samples appears to decrease as the radiation dose increases. Beyond a radiation dose of 15 kGy, the doublet S 2p photoelectron lines exhibit a decrease in intensity of approximately 4-fold compared to their corresponding photoelectron lines intensities in the bare Sb₂S₃ sample. The observation that the photoelectron line shows an intensity change over 15 kGy indicates a significant influence on the electronic structure of Sb₂S₃ films. This threshold behavior highlights the need for careful consideration of irradiation doses in understanding and controlling the electronic properties of the Sb₂S₃ material. We speculate two main factors that contribute to this behavior: (i) the decrease in the number of sulfur sites on the Sb₂S₃ surface with increasing γ irradiation; and (ii) the presence of an ionization process in the experimental setup.41 Consequently, the radiation could induce an increase of S vacancies in the Sb₂S₃ structure. Likewise, the XPS spectrum of the Sb 3d_{5/2} photoelectron line shows a broader peak before the irradiation, which decreases in intensity after the

Paper

(a) **(b)** S_{2p} 3 d _{5/2} Sb 3d intensity (a.u.) Intensity (a.u.) S 2p_{3/2} 3 d _{3/2} S 2p_{1/2} 163 162 161 160 159 545 535 530 525 520 158

Fig. 4 High-resolution XPS spectra of (a) S 2p and (b) Sb 3d core levels of the bare Sb_2S_3 material.

Binding Energy (eV)

irradiation without any significant shifting in their BE positions, as illustrated in Fig. 5(b)-(f). The observed sharpening of the Sb 3d_{5/2} peaks is attributed to a reduction in the oxygen content in the Sb_2S_3 samples after γ irradiation. A common problem when analyzing Sb-XPS data is the possibility of overlap between the photoelectron lines of Sb 3d and O 1s.42 To resolve overlapping photoelectron lines in the Sb-XPS survey spectrum, we employed the deconvolution process using Origin software to determine the various elemental concentrations. Through spectral analysis of the Sb-XPS data, we found that fitting the photoelectron lines using Voigt functions provides a more accurate representation of the oxidation states. In the case of a bare sample, some of the O 1s and Sb 3d_{5/2} photoelectron lines typically merge and form a broader width peak. However, the loss of oxygen from the Sb₂S₃ samples during y irradiation leads to a decrease of full width at half maximum (FWHM), as shown in Table 1. This result exhibits a reduction of Sb 3d_{5/2} photoelectron lines, potentially attributed to the decrease in oxygen vacancies. On the other hand, the surface atomic ratio of Sb/O is calculated following this formula Integrated area of Sb peak


in the XPS spectra. As can be Integrated area of O peak seen, the surface atomic ratio of Sb/O exhibited a gradual increase with higher radiation doses. The atomic ratio of Sb/O estimated from the surface area in the bare sample is approximately 1.21, which is significantly lower than the sample exposed to a radiation dose of 20 kGy, where the atomic ratio is 1.35. This can be attributed to the annihilation of microcrystalline Sb oxide species formed on the surface at these elevated doses. A similar result has been reported for Y₁Ba₂Cu₃O_{7-δ} superconductors, where γ radiation was used to decrease the oxygen level.⁴³ Moreover, there is a decreasing trend in the intensity of the Sb $3d_{5/2}$ photoelectron line following γ irradiation. In comparison to a bare sample, the intensity of this photoelectron line is significantly decreased by a factor of five when exposed to an irradiation dose of 15 kGy. These alterations in photoelectron line intensity are likely the result of changes in element levels induced by γ irradiation. Such changes could be ascribed to bond breaking and subsequent reorganization in the Sb₂S₃

samples. It is also plausible that the variation in element contents in the Sb₂S₃ sample is due to the diffusion of ions from the surface to the bulk material and vice versa, as well as the decrease in oxygen content after γ irradiation. In this regard, the likelihood of a change in Sb content due to a change in the oxidation state from Sb5+ to Sb3+ is excluded since such changes are not stable and recover quickly.44 Overall, the results of the XPS measurements reveal the formation of S vacancies and loss of oxygen content in the irradiated samples. Thus, the charge carrier separation could have occurred in the irradiated samples. Our results are consistent with those of Wang et al. who found that S vacancies introduced by γ-irradiation on the Zn side can accelerate the separation of charge carriers by trapping electrons that are transferred to the catalyst surface.27 In line with XPS analysis, ICP-AES further investigates the atomic proportions of bare and irradiated samples, as shown in Table 2. By comparing the atomic proportions of all samples, the ICP-AES result is consistent with the results of the XPS analysis and confirms the accuracy of the elemental composition of the material.

Binding energy (eV)

3.2 Structural properties

The crystalline structure and phase purity of the bare and irradiated Sb₂S₃ thin films were characterized by X-ray diffraction (XRD) from $2\theta = 10^{\circ}$ to $2\theta = 60^{\circ}$. Fig. 6 shows the XRD patterns of bare and irradiated thin films exposed to various γ ray energies. XRD peaks of the samples are in good agreement with the orthorhombic crystal structure of Sb₂S₃ (stibnite)⁴⁵ with the lattice constants a = 11.310 Å, b = 3.836 Å, c = 11.228 Å and Pbnmspace group symmetry, which is in line with the literature values of the standard JCPDS card no: 42-1393. What is more, there are no impurities or unwanted phases present in the XRD patterns as the γ ray energies increase. This indicates that the material's crystalline structure remains relatively stable under the influence of gamma radiation. The other diffraction peaks indexed by hashtags stand for ITO glass substrate (JCPDS 06-0416). It is worth noting that the intensity of the prominent peaks located at $2\theta = 17,52^{\circ}, 2\theta = 24,88^{\circ}, \text{ and } 2\theta = 29,24^{\circ} \text{ gradually increases}$ with increasing gamma irradiation, and the FWHM of the

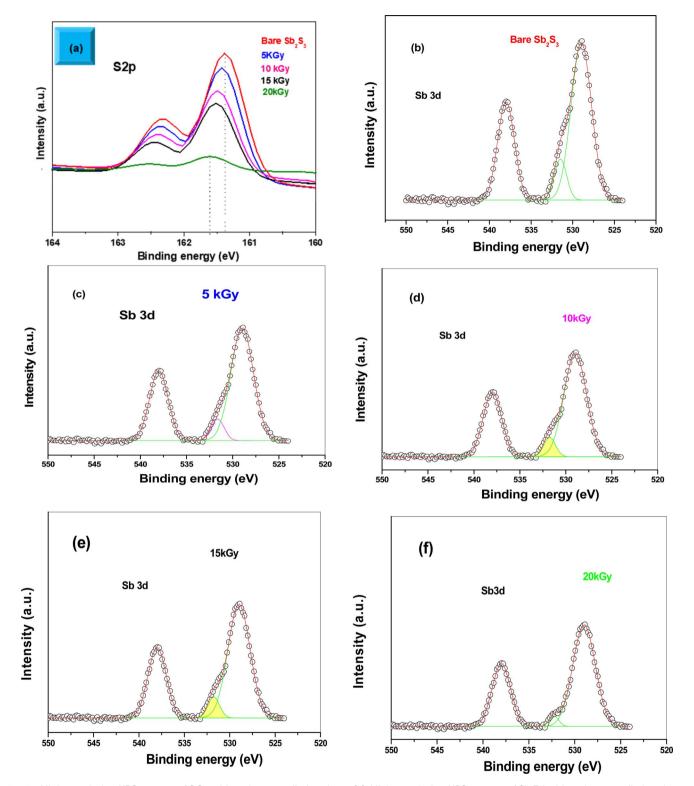

High-resolution XPS spectra of S 2p with various γ radiation doses (a). High-resolution XPS spectra of Sb 3d with various γ radiation doses (b-f).

diffraction peaks decreases up to irradiation dose of 15 kGy. However, above this value, the peak intensity decreases and the FWHM increases slightly due to the structural disorder created after the irradiation process. The initial intensification and the sharpening of the peak intensity with γ -ray irradiations can be attributed to an enhancement in crystallinity. However, the reduction is attributed to the impact of ionizing γ -ray irradiations, allowing Sb and S atoms to be shifted and the molecules to

Table 1 FWHM of $3d_{5/2}$ photoelectron line as a function of gamma irradiation dose

Gamma irradiation dose (kGy)	FWHM (eV)
0	2.20
5	2.16
10	2.12
15	1.90
20	2.15

Table 2 Composition of different films from ICP-AES data

Gamma irradiation dose (kGy)	Sb (at%)	S (at%)	Total
0	38.92	61.08	100
5	39.15	60.85	100
10	39.46	60.54	100
15	40.80	59.20	100
20	38.41	61.59	100

be broken down. A similar effect has previously been described for WO₃ thin films grown by RF sputtering. ⁴⁶ This suggests that the gamma irradiation process might have positively influenced the charge carrier dynamics within the Sb₂S₃ material. Understanding and harnessing such effects could have significant implications for the development of efficient photocatalysts for PEC cells. Our findings are somewhat surprising since γ -ray radiations are supposed to generate structural defects, disordering and clustering, swelling, and polygonization leading to a drop in peak intensity. ⁴⁷ Nevertheless, γ -ray irradiations could induce a self-annealing process in the Sb₂S₃ films by increasing

the kinetic energy of atoms, subsequently an improvement in crystal quality. These observations agree well with previously reported results for irradiated semiconductors.48 The enhanced crystal structure leads to higher charge transfer mobility and light absorption. 49 In this regard, γ ray energy could improve the crystallinity of the Sb₂S₃ films and promote its PEC properties. It is also worthwhile to note that the orthorhombic crystal structure and diffraction angles of Sb₂S₃ films did not change after γ-ray irradiation. This implies that Sb₂S₃ films have structural integrity even after γ-ray irradiations. Such results indicate that Sb₂S₃ has notable bonding strength and high γ-ray hardness. Other semiconductor materials that have been significantly spoiled by γ irradiation have not demonstrated such resilience. 50 To further investigate the XRD measurements, the FWHM of the dominant peak (310) and the average crystallite size versus of γ irradiation dose was calculated for all the samples. Note that the FWHM of the peak was found by fitting the XRD patterns using Origin software. The data on the structural characteristics of the Sb₂S₃ thin films were estimated by computing the average crystallite size (D), the lattice strain (ε), as well as the dislocation density (δ) according to the following equations:

$$\langle D \rangle = \frac{K\lambda}{\beta(2\theta)\cos\theta_{310}} \tag{5}$$

$$\varepsilon = \frac{\beta \cos \theta - \frac{\lambda}{D}}{\sin \theta} \tag{6}$$

$$\delta = \frac{1}{\langle D \rangle^2} \tag{7}$$

where λ is the wavelength of incident X-ray radiation (1.5406 Å of CuK_{α}), β is FWHM, θ is the Bragg's angle in radians, and K

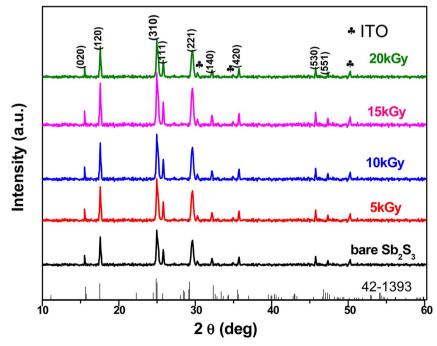


Fig. 6 XRD pattern of Sb₂S₃ before and after irradiation with various γ radiation doses.

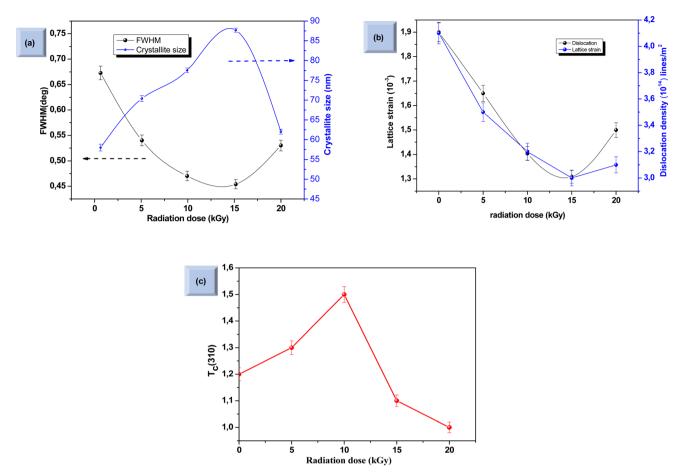


Fig. 7 Variation of full width at half maximum (FWHM) and crystallite size as a function of irradiation doses (a). Variation of dislocation density (δ) and lattice strain at different irradiation doses (b). Influence of γ radiation on texture coefficient T_c (310) (c). Each data point in the two graphs is accompanied by error bars that represent a 2% margin of uncertainty and provide a quantifiable measure of the variability in our measurements.

can have values anywhere from 0.62 and 2.08. In this paper, K=0.9 was used. As shown in Fig. 7a, increasing the γ irradiation dose results in a decrease in FWHM from 0.67° to 0.45° when the irradiation dose varies between 0 and 15 kGy. The average crystallite size reaches its maximum value of 87.4 nm at a γ radiation dose of 15 kGy. Conversely, with an increase in γ -radiation dose up to 15 kGy, the dislocation density and lattice strain of Sb₂S₃ thin films decrease. Subsequently, beyond 15 kGy, they increase, as shown in Fig. 7b. The increase in crystallite size and reduction in GBs, lattice strain, and dislocation density with the increase in γ -radiation dose suggest improvements in crystal lattice quality. This is often accompanied by a more orderly and error-free structure of the Sb₂S₃ thin films.

The texture coefficient $T_c(hkl)$ is a parameter used to quantify the preferred orientation of a plane (hkl) and is estimated using the following equation:

$$T_{c}(310) = \frac{\frac{I_{(310)}}{I_{0(310)}}}{\frac{1}{N} \sum_{n} \frac{I_{(hkl)}}{I_{0(hkl)}}}$$
(8)

where $I_{(310)}$ and $I_{(hkl)}$ are the intensities of the (310) crystal plane and a general peak with Miller indices (hkl), respectively. $I_{0(310)}$ and $I_{0(hkl)}$ are the integrated intensities of the JCPDS (powder

diffraction pattern) data of the corresponding plane (310) and (hkl) of the Sb₂S₃ material, respectively. N is the number of reflection peaks, and n = 9 is the number of diffraction peaks measured in the analysis. When T_c (310) = 1 that means no preferred orientation (i.e., the crystallites are randomly oriented), while a $T_c(310) > 1$ indicates the preferred orientation of the crystallites is in (310) direction. A T_c (310) < 1 means that the [310] orientation is less preferred than in a randomly oriented sample. Fig. 7c shows that most films have a $T_c > 1$, indicating the presence of preferred (310)-oriented crystallites that increase with γ radiation compared to the bare Sb₂S₃ sample. These results indicate that γ radiation can confirm the Sb₂S₃ crystal orientation of the preferred [310] orientation. Such preferential orientation was previously observed for Sb₂S₃ thin films deposited using vapor transport deposition methods,⁵¹ and solvothermal method.52 To further scrutinize the phase purity of Sb₂S₃ material, Raman measurement was performed on the deposited thin films at room temperature. Fig. 8 depicts the Raman spectra collected before and after irradiations between wavenumbers of 100-350 cm⁻¹ at different radiation doses. The bands located at 150, 280, and 310 cm⁻¹ can be assigned to specific vibrational modes related to the orthorhombic Sb₂S₃ phase corresponding to Sb-Sb bond, antisymmetric Sb-S stretch, and symmetric Sb-S stretch in

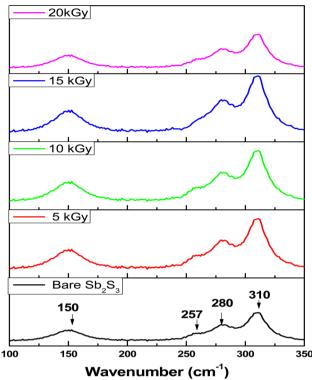


Fig. 8 Typical micro-Raman spectra before and after irradiation with different irradiation doses.

orthorhombic Sb_2S_3 phase, respectively.⁵³ The bands located at 280 cm⁻¹ and 310 cm⁻¹ were attributed to the symmetric vibrations of a C3v symmetric cone element, as reported in previous studies.⁵⁴ The spectrum of the bare sample reveals also a weak band located around 257 cm⁻¹ suggesting the presence of Sb_2O_3 ,⁵⁵ which corroborates the XPS results.

The weak band at 257 cm⁻¹ reduces with increasing gamma radiation exposure; however, it never completely disappears due to the residual Sb₂O₃ phase present in the synthesized material. Thus, when the surface defects are created owing to γ irradiation, the oxygen present in the environment interacts with these defects leading to the formation of Sb2O3. Nevertheless, the existence of the Sb₂O₃ phases could not be observed in the XRD pattern. This discrepancy between XRD and Raman results would be due to chemical sensitivity. XRD can give information about the arrangement of atoms, but it might not distinguish between different chemical species that have similar crystal structures. It is worth noting that no bands belonging to other foreign phases or impurities such as S₈, and SbS₃ were detected, suggesting moderately high purity of the formed Sb₂S₃ thin film. On the other hand, the band intensity of the Raman spectra increased significantly when the irradiation dose increased up to 15 kGy without any shift. This implies that ionizing energy might strengthen the Sb₂S₃ orthorhombic crystal structure and improve its quality, which is in line with the XRD results. In addition, the Sb₂O₃ phase gradually vanishes, signifying a purer fabricated Sb₂S₃ film. As a result, Sb₂S₃ thin films after the ionizing radiation process are almost free of Sb₂O₃ phases with a sulfur vacancy.

3.3 Scanning electron microscope (SEM) measurements

To unearth the impact of γ-irradiation on the surface morphology of the synthesized photoelectrodes, we conducted SEM measurements on Sb₂S₃ films and analyzed the quantification of grain sizes. As depicted in Fig. 9, the impact of γirradiation below 15 kGy conspicuously increases the grain size. Meanwhile, the compactness and surface smoothness of film were boosted greatly with increasing γ -irradiation doses. The corresponding histograms illustrating the size distribution of the Sb₂S₃ grains are presented in Fig. 9. For the film irradiated with 15 kGy, it demonstrates an average size of about 151 nm. However, beyond this dose, the grain size of the film decreases and its compactness deteriorates. It is also worthwhile to note that the voids and shape irregularities observed in the asdeposited thin film have been significantly reduced compared to irradiated films. They are substituted by more regular grain shapes, resulting in a reduction in GBs. This observation is consistent with the enhancement of crystallinity in the irradiated thin film, as described earlier through XRD analysis.

3.4 Atomic force microscopy (AFM) measurements

AFM with a contact mode was utilized to depict the 2D morphology of all Sb₂S₃ samples grown on an ITO substrate with a scanning area of 1 μ m \times 1 μ m under various γ -irradiation doses ranging from 0 to 20 kGy. As depicted in Fig. 10(a)-(e), the morphology of the examined films is significantly influenced by the γ-irradiation. Fig. 10a shows the morphology of the bare Sb₂S₃ film with random grains and spherical shapes, but not uniformly distributed across the entire surface. Nevertheless, as the dose increases, the topography of the Sb₂S₃ film changes, and more spherical particles become evident, as displayed in Fig. 10(b)-(e). Indeed, γ-irradiation can induce changes in the material properties, such as compaction or densification. This can cause the spherical shapes to become more compact and spherical in appearance when imaged with AFM. The average grain size of Sb₂S₃ films gradually increased with γ -irradiation doses and reached its maximum at 180 nm, as shown in Table 3. The grain sizes estimated by AFM measurements are somewhat larger than those determined by the Scherrer equation. The overestimated grain size values can be attributed to the fact that AFM measurements directly capture the surface morphology of agglomerated grains and thus provide information about the particle size. The obtained average grain size can improve the optical scattering by increasing the absorption coefficient, and this can also affect the film resistivity. On the other hand, the RMS of the surface roughness R_q is an important parameter that provides a measure of the average magnitude of surface deviations from the mean plane⁵⁶ and is computed using the following equation:

$$R_{\rm q} = \sqrt{\frac{1}{N} \sum_{j=1}^{N} \left(Z_j - \tilde{Z} \right)^2} \tag{9}$$

where N, Z_j , and \tilde{Z} are the number of points within the given area, the height deviation of each data point, and the mean height,

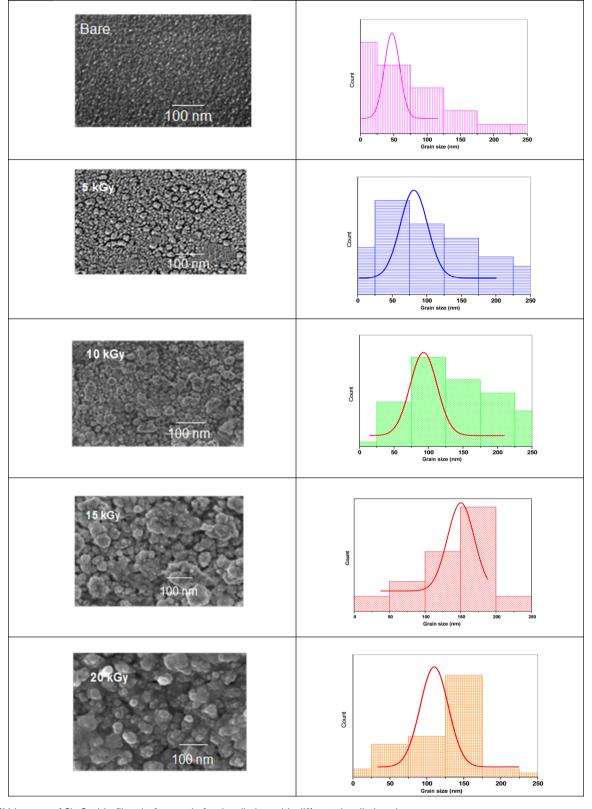


Fig. 9 SEM images of Sb_2S_3 thin films before and after irradiation with different irradiation doses.

respectively. Table 3 exhibits the variation of $R_{\rm q}$ *versus* the γ -radiation dose. The RMS surface roughness increases progressively and reaches its maximum value of about 38 nm for

the irradiated sample with 15 kGy film. With an increase in gamma irradiation at a dose of 20 kGy, the $R_{\rm q}$ value decreases to about 30 nm because more defects and sulfur vacancies appear

Table 3 RMS surface roughness as a function of gamma irradiation dose

Gamma irradiation dose (kGy)	RMS surface roughness	Average grain size of Sb ₂ S ₃ (nm)
0	15	124
5	21	145
10	29	168
15	38	180
20	30	171

on the surface. From the obtained AFM results of $\mathrm{Sb_2S_3}$ samples, the variation of R_q is consistent with the variation of crystallite size from XRD analysis. It is established that an increase in surface roughness results in a higher number of active sites on the surface, and the GBs become smaller. This morphology is beneficial for PEC performance⁵⁷ since it suppresses the recombination of excitonic pairs. A rougher film surface is expected to have a larger electrode/electrolyte interface area, thereby increasing the rate of charge transport relative to recombination.

3.5 Hall effect measurement

Hall effect measurement is a straightforward method for determining majority carrier density, electrical conductivity, and Hall mobility (μ_{HALL}) in semiconductor materials. It was used for both bare and irradiated Sb₂S₃ films synthesized on the ITO substrate under consistent conditions including a constant electric current of 10 μ A and a constant magnetic field of about 0.5 T using Van der Pauw geometry at room temperature. It is interesting to note that gamma irradiation does not seem to have a discernible impact on the electrical conductivity type of the Sb₂S₃ films, which consistently exhibit p-type behavior

across different irradiation doses. Thus, there is no transition from p-type to n-type conductivity under gamma irradiation. However, it is worth noting that gamma irradiation may impact other parameters of Hall effect measurements charge carrier mobility (μ_H) , charge density (N), Hall coefficient (R_H) , and resistivity (ρ). The p-type conductivity observed in the obtained Sb₂S₃ films is attributed to sulfur loss, as discussed earlier in the XPS section. This correlation between the sulfur loss and the resulting p-type conductivity aligns with previously reported research on Sb₂S₃ thin films.⁵⁸ It is worth noting that p-type conductivity for Sb₂S₃ is often reported in the literature, whereas n-type behavior is rarely reported.¹⁷ According to the first principles of density functional theory (DFT), the Sb₂S₃ films exhibit p-type semiconductor character due to S-on-Sb antisite (SSb) and to the S-vacancies. 59 While Rajpure et al. 60 showed that the electrical conductivity in Sb₂S₃ switches from ntype to p-type only by modifying the precursor solvent from an aqueous to a non-aqueous solution. Fig. 11 illustrates the effect of γ irradiation on the electrical resistivity (ρ), hole density ($N_{\rm h}$), and hole mobility (μ_{HALL}). The electrical resistivity tends to decrease versus γ irradiation dose in the range of 0-15 kGy. When the γ irradiation doses increase, the electrical resistivity declines gradually from $8 \times 10^5 \Omega$ cm (0 kGy) to $4 \times 10^5 \Omega$ cm (15 kGy), which means the electrical conductivity increases. The obtained results can be attributed to the improved crystalline quality and the lack of trap states (SSb and VSb), providing support for the observed increase in the conductivity of the Sb₂S₃ layers. Recent studies have demonstrated that the electrical properties of Sb₂S₃-based thin films are significantly influenced by the crystallographic orientation of the polycrystalline domains.61 This suggests an intrinsic connection between the electrical properties of these materials and their

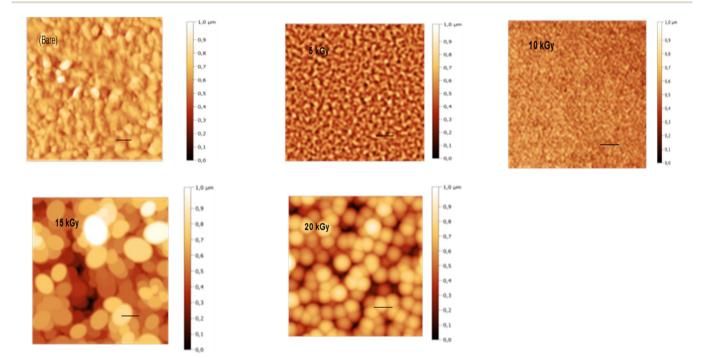


Fig. 10 2D AFM micrographs of bare and irradiated Sb₂S₃ thin films at different doses. The scale bar on all images indicates a length of 100 nm.

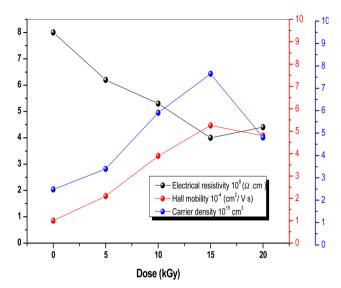


Fig. 11 Electrical resistivity, Hall mobility, and carrier density of Sb_2S_3 thin films before and after γ -irradiation with different doses.

crystalline structures and morphologies. Normal grain growth was observed when the grains were vertically stacked on the bonded substrates through effective covalent Sb–S bonds, resulting in [hk1]-oriented films, which are useful for charge carrier transport along the perpendicular direction. Carrier transport along the perpendicular direction. Find contrast, γ irradiation promoted abnormal $[Sb_4S_6]_n$ ribbons grain growth with parallel orientation to the substrates through weak van der Waals forces, thereby favoring [hk0]-oriented Sb_2S_3 film growth. Hence, it can be inferred that the Sb_2S_3 thin film with the preferred [310] orientation enables higher conductivity and more efficient separation of a photogenerated carrier in the corresponding PEC device compared to the typically [hk1]-oriented films. According to Vadapoo $et\ al.$ the conductivity of

Sb₂S₃ film at room temperature is 100-fold smaller along the perpendicular (Sb₄S₆)_n ribbon direction than in the parallel direction.63 Therefore, it is believed that gamma irradiation could induce a preferential crystallographic direction and improve the conductivity of Sb₂S₃ films more efficiently. On the other hand, with increasing irradiation dose up to 15 kGy, μ_{HALL} consistently raises from 10^{-4} cm² V⁻¹ s⁻¹ to 5.25 10^{-4} cm² V⁻¹ $\rm s^{-1}$, and the hole density raises from 2.48 \times 10¹⁵ cm³ to 7.65 \times 10¹⁵ cm³. This increase in carrier mobility and hole density could be related to an improvement in microstructure and morphology as shown by AFM studies. Nevertheless, above a dose of 15 kGy, the electrical resistivity increases, the electron density decreases, and μ_{HALL} drops to a value of about 3.75 \times 10⁻⁴ cm² V⁻¹ s⁻¹. This could be described by the fact that excessive γ-irradiation may generate too many lattice defects, such as dislocations and/or GBs acting as electron-hole recombination centers.64 Finally, our results suggest that irradiation is a promising method for maintaining electrical conductivity type, however, its variability at various doses could be employed as a potential technique for detecting ionizing radiation.

3.6 Optical absorption properties

3.6.1 UV-VIS spectroscopic measurements. Fig. 12a exhibits the optical absorption spectra of bare and irradiated $\mathrm{Sb}_2\mathrm{S}_3$ films in the photon energy range of 1 eV to 2.25 eV. The linear optical absorption coefficient $\alpha(\lambda)$ was estimated from the transmittance and the reflectance spectra in the strong absorption region and achieved by the well-known equation:

$$\alpha(\lambda) = \frac{1}{d} \ln \left(\frac{(1-R)^2 + \left((1-R)^4 + 4R^2T^2\right)^{1/2}}{2T} \right)$$
 (10)

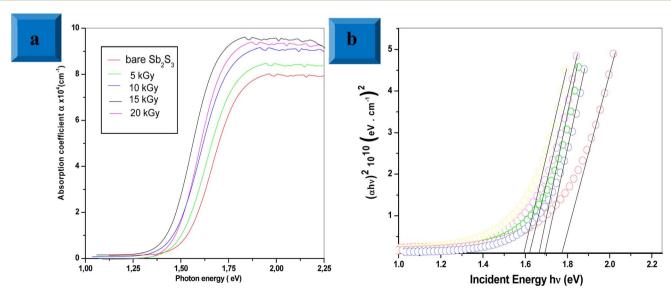


Fig. 12 UV-vis absorption spectra for bare and irradiated Sb_2S_3 thin films at different doses (a). Tauc plot for bare and irradiated samples was obtained from the absorption spectra; the solid lines represent the linear regressions on the data from which the optical band gap energies were determined (b).

Paper

where d is the thickness of the deposited films, R and T are the reflectance and transmittance, respectively. The results show that the average absorption coefficient gradually increases with increasing irradiation doses. Especially, the irradiated 15 kGy $\mathrm{Sb_2S_3}$ film exhibits a higher absorption coefficient. This increase could be attributed to the enhancement of crystallinity as discussed above in the XRD section. On the other hand, the optical band gap energy for all the $\mathrm{Sb_2S_3}$ films is estimated from Tauc plot using the following equation:

$$(\alpha h \nu) = A(h \nu - E_{g})^{n} \tag{11}$$

where α , A, h, ν , $E_{\rm g}$ and n stand for absorption coefficient, a constant parameter, Planck's constant, the frequency of incident light, the optical band gap energy, and n constant linked to the type of optical transition (n = 2 for indirect band gap and n= 1/2 for direct band gap), respectively. So, we plot the variation of $(\alpha h \nu)$ as a function of $(h \nu)^{1/2}$, then we fit the linear portion of the curve and extend it to the x-axis for all synthesized samples. Upon γ irradiation, the optical band gap is found to gradually decrease from 1.78 eV to 1.60 eV until radiation dose of 15 kGy and marginally increases at 1.64 eV, thereafter, as shown in Fig. 12b. The initial red shift in the optical band gap value suggests that gamma irradiation introduces additional electrons, causing the Fermi level to rise. The rise in the Fermi level results in the formation of impurity energy levels at the bottom of the conduction band or valence band, potentially leading to enhanced catalytic activity upon photoexcitation. Similar effects have been reported by other studies. 65 Considering the forecast band gap of 15 kGy Sb₂S₃ film, it is a prone candidate for use in a photoelectrochemical cell. It is well known that a single semiconductor with a bandgap of 1.60 eV can achieve a maximum STH efficiency of 30% at one solar irradiance.66 However, for a higher irradiation dose above 15 kGy, the broadening of the band gap could be explained by the energy width of band tails of the localized state. Therefore, further irradiation dose by over 15 kGy could not decrease the band gap any further but controversy the band gap increases at 1.64 eV.

3.6.2 Photoluminescence spectroscopy. Photoluminescence (PL) is a non-destructive technique for probing defects and electronic properties in semiconductor materials. Fig. 13 shows the dose-dependent PL emission spectra for bare and γ-irradiated Sb₂S₃ films scrutinized with an excited laser wavelength of 266 nm. The PL emission spectra of bare film showed a narrow band with a peak around 696 nm (corresponding to 1.78 eV) and a wide emission peak at 885 nm wavelength (corresponding to 1.40 eV). This first band is attributed to the band-to-band emission of Sb₂S₃, roughly in line with the conclusions drawn from UV-VIS spectroscopic measurements, while the second band could be ascribed to the state of vacancies or defects in Sb₂S₃ films.⁶⁷ Recently, Krautmann et al. have reported a similar variation of room temperature PL analysis of the synthesized Sb₂S₃ films by close-spaced sublimation, where they found two PL peaks located at 1.72 eV and 1.40 eV.68 Meanwhile, Aslan et al. performed PL analysis for dip-coating Sb₂S₃ films photodetector. Therein the authors have found three PL emissions peaks located at 400, 521, and

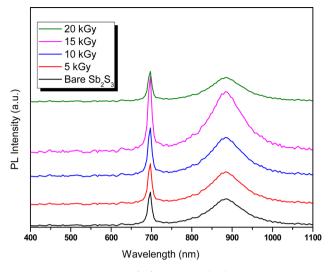




Fig. 13 Photoluminescence (PL) spectra of Sb_2S_3 thin films before and after γ -irradiation with different doses.


652.5 nm.69 The slim contrast in the values of the PL emission peaks would be attributed to lattice distortion caused by γ rays. On the other hand, we note the increase in PL intensity with increasing irradiation doses. Especially, the film exposed to a dose of 15 kGy exhibits the greatest PL intensity, which is 2.2 orders of magnitude greater than that of the unexposed film. The increase in PL intensity upon irradiation could be due to the fusion and agglomeration of particles, resulting in the formation of larger grains, which can effectively annihilate the surface defects and consequently reduce non-radiative recombination losses and raise radiative emission. Furthermore, it should be noted that a broadening of γ-irradiated thin films compared to bare Sb₂S₃ sample is observed due to inhomogeneous particle size and to self-trapped exciton states induced by the lattice distortions and surface defects. At 20 kGy, a reduced PL intensity is observed compared to the other samples, suggesting increased non-radiative recombination, although this sample has the lowest FWHM.


3.7 Wettability analysis

Wettability tests were used to measure the ability of a water droplet to spread and adhere to a solid surface. The CA formed by a drop on a solid surface is a crucial parameter for evaluating wettability and can be influenced by various factors, including surface tension, surface roughness, and chemical composition.70 A low CA (close to 0°) indicates high wettability or hydrophilicity, while a high CA (close to 180°) indicates low wettability or hydrophobicity. As a matter of fact, γ radiations can alter the CA and surface wetting behavior, which is a crucial aspect for efficient H₂ production in aqueous solution. In this context, the surface wettability of the Sb₂S₃ thin film was investigated at various γ-irradiation doses. As illustrated in Fig. 14, all the samples exhibit a CA greater than 90°, suggesting low wettability and consequently resulting in a low Gibbs surface free energy.71 The CA decreases from 145.2° to 110.8° with increasing gamma irradiation, which may affect the












Fig. 14 Water contact angle of as-deposited and γ -irradiated Sb₂S₃ thin films with different doses.

electrolyte absorption and the interaction between Sb₂S₃ photoelectrodes and electrolytes. The optimal CA was noted for the sample irradiated with a dose of 15 kGy, signifying a higher surface wettability. The observations also agree with the results of the AFM measurements. In fact, lower CA corresponds to higher surface roughness. It is known that chalcogenide materials typically consist of elements with similar electronegativity that form a nonpolar covalent bond, resulting in a hydrophobic surface.72 These hydrophobic properties with rough surfaces generated by γ irradiations tend to trap air pockets, impeding complete wetting by the water drop. This obtained low CA has a positive effect on improving the adsorption surface between the Sb₂S₃ thin film and the water drop. An enhancement in PEC performance is expected for the specific film treated with a dose of 15 kGy, as this condition allowed further improvement in surface hydrophilicity.

3.8 Photoelectrochemical measurements

To elucidate the effect of γ radiations on the PEC properties of Sb_2S_3 photoelectrodes, photocurrent density-voltage (I-V) tests were carried out under chopped white LED illumination using a standard three-electrode cell in an aqueous sodium sulfate solution (Na₂SO₄) with a concentration of 0.5 mol L⁻¹ and a pH \cong 7. The active surface area of the working electrode was set at ca. 0.16 cm², and the counter electrode used was Pt. Fig. 15a exhibits representative chopped (dark/light) linear sweep voltammetry (LSV) scans of bare and irradiated Sb2S3 samples from -0.2 to 0.2 V vs. RHE with a periodic time of 1 s light on/off. Since there is a negligible current density on all photoelectrodes in dark lighting conditions, this is not displayed. By the way, no anodic transient current was detected during the entire measurement period that would be responsible for back electron transfer when the light was turned off. In striking contrast, all Sb₂S₃ photoelectrodes produced cathodic photocurrents upon illumination, corroborating the p-type conductivity of Sb₂S₃ films determined by Hall effect measurement. The onset potentials of all photocathodes were approximately

0.15 V vs. RHE. For comparison, other encouraging photocathodes like Cu₂ZnSnS₄, CuO, and Si typically exhibit a photocurrent onset at around 0.7 V vs. RHE for water reduction.73 However, similarly high photocurrent onset potentials have recently been stated for CuBi₂O₄ and Cu₂O.⁷⁴ During the intermittent illumination periods, there is very little leakage current, as demonstrated by the noticeable increase and decrease in photocurrent density upon exposure to light.²² The obtained results of the transient photocurrent response certainly corroborated that the photocurrent density generated from the irradiated Sb₂S₃ photocathodes was meaningfully higher than that of the bare photocathode owing to the existence of a charge transport mechanism in the irradiated Sb₂S₃ samples. The bare sample shows the lowest transient photocurrent responses of ca. 0.60 mA cm⁻² at 0 V vs. RHE, indicating the highest recombination rate of photogenerated excitonic pairs, as well as the significantly inadequate electron mobility in the Sb₂S₃ film. The obtained photocurrent density of the bare photocathode aligns with findings from other reports. 75 Comparatively, Sb₂S₃ subjected to a dose of 15 kGy shows the strongest photo-current density, reaching a value of 1.62 mA cm⁻² at 0 V vs. RHE. This magnitude is almost 2.7 times higher than that of the bare sample, indicating a notable enhancement in the efficiency of photogenerated charge separation. The rise in photocurrent density is attributed to the increased number of sulfur vacancies generated by y radiations, which facilitates the capture of electrons from the conduction band of Sb₂S₃ and thus improves the charge separation ability. The introduction of vacancies in semiconductors could have multiple effects on their properties. Indeed, vacancies can improve photo absorption capabilities, acting as traps for photogenerated electrons, which helps limit the recombination of excitonic pairs.76 This phenomenon contributes to enhanced photo reactivity in semiconductor materials. However, a higher irradiation dose (>15 kGy) may create more bulk vacancies, resulting in a lower photocurrent density. These defects and traps within the photocathode acted as recombination centers and led to a reduction in

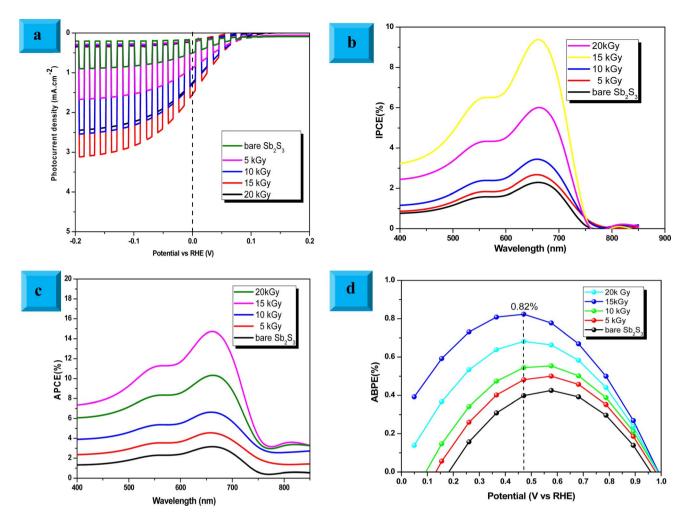


Fig. 15 (a) Linear sweep voltammetry (LSV) plots of the bare and irradiated Sb_2S_3 -based photocathodes. (b) The incident photocurrent conversion efficiencies (IPCEs) spectra were recorded for Sb_2S_3 -based photocathodes with an applied bias voltage of 0 V vs. RHE under front illumination. (c) Absorbed photon-to-current efficiency (APCE) spectra were recorded for all Sb_2S_3 -based photocathodes. (d) Calculated applied bias photon-to-current efficiency (ABPE) for all Sb_2S_3 -based photocathodes. All measurements were carried out in 0.5 M Na_2SO_4 buffer (pH \cong 7) electrolyte.

photocurrent density. To assess the charge separation efficiency of the irradiated Sb₂S₃-based photocathodes in comparison to the bare one, the IPCE and APCE of all photocathodes were then measured in the wavelength spectrum ranging from 400 nm to 900 nm under front illumination with an applied bias voltage of 0 V vs. RHE. The wavelength dependence of the IPCE and APCE of Sb₂S₃-based photocathodes with different γ radiation doses is shown in Fig. 15b and c. The IPCE and APCE values of the photocathode irradiated with 15 kGy are significantly higher than the other photocathodes. They exhibit an IPCE peak and an APCE peak at 648 nm, with values of 9.35% and 14.47%, respectively. This means that the optimized sample has a higher quantum efficiency than the other ones. The dependence of the IPCE and APCE performance on the irradiation dose is attributed to the band gap of the irradiated films since significant variations were also found in the absorption spectra. This correlation can be attributed to the ease of transporting photocarriers through the multilayers in this Sb₂S₃ structure, as the enhancement in conversion efficiency depends on the

absorption of the incident photons and the transmission of the photogenerated carriers to reach the surface for the chemical reaction. A possible reason for the loss of efficiency above a dose of 15 kGy is ascribed to the low crystallinity of Sb₂S₃ films and imperfect interfaces, which lead to high recombination rates. The limited photoconversion performance in terms of IPCE and APCE at λ over 756 nm is consistent with the optical band gap of irradiated Sb₂S₃ semiconductors, which primarily absorb light to generate electrons and holes for the PEC charge transfer reaction across their surface. What is more, to fully evaluate the PEC water-splitting performance of all photocathodes, we measured the ABPE, which is related to the amount of energy used during the process.⁷⁷ Fig. 15d displays the APBE of the synthesized photocathodes. The maximum efficiency of the 15 kGy-irradiated sample was 0.82% at 0.47 V vs. RHE, which was significantly lower than other irradiated samples. 15 kGyirradiated sample exhibited the lowest potential and higher efficiency, suggesting superior PEC water splitting performance compared to other samples. The enhanced ABPE of the

optimized sample is due to the boosted visible light resulting in improved exciton dissociation and transfer. It is worth noting that the optimized photocathode increases the conversion efficiency while decreasing the required potential to achieve the maximum photoconversion efficiency. Meanwhile, to acquire a deeper understanding of the charge transfer and separation processes in all Sb₂S₃ samples, M–S analysis was conducted. The carrier concentration and flat band potential ($V_{\rm fb}$) were estimated from the slope of a plot of $1/C^2$ vs. V, and the x-intercept of the extrapolated linear segment of the M–S plot, respectively. The calculation was based on the following relationship:

$$\frac{1}{C_{\rm sc}^2} = \frac{2}{A^2 \varepsilon_0 \varepsilon_{\rm r} q N} \left[\pm \left(V - V_{\rm fb} \right) - \frac{k_{\rm B} T}{q} \right] \tag{12}$$

where $C_{\rm sc}$ is space charge capacitance (F), q is an elementary charge (1.6 \times 10⁻¹⁹ C), A is electrode surface area (cm²), $\varepsilon_{\rm r}$ = 6.67 is the relative permittivity of Sb_2S_3 , 78 ε_0 is vacuum permittivity (8.854 \times 10⁻¹² F m⁻¹), N is carrier concentration in the semiconductor (cm $^{-3}$), V is applied potential (V), V_{fb} is flat band potential (V), and $k_{\rm B}$ is Boltzmann constant (1.38 \times 10⁻²³ J K⁻¹), and T is the absolute temperature (K). $\frac{1}{C_{sc}^{2}}$ decreases with the applied bias voltage in the presence of a space charge region, confirming the p-type semiconductor behavior for all samples, as shown in Fig. 16. In addition, γ irradiation does not affect the p-type character of the Sb₂S₃ semiconductor, echoing the aforementioned (J-V) measurements. The result obtained is in good agreement with the findings from previous research studies. 79 In addition, the acceptor density (N_A) estimated from the slopes of M-S plots increases from $2.8 \times 10^{15} \text{ cm}^3$ (bare film) to 4.6 \times 10¹⁵ cm³ (15 kGy irradiated film) and then decreases to 3.1×10^{15} cm³ when the irradiation doses reach 20 kGy. The changes in acceptor density can be attributed to the

sulfur vacancies caused by γ -irradiation. The 15 kGy films exhibited a significantly higher acceptor density compared to the bare sample. This increase occurred despite no major changes in the phase structure of the Sb₂S₃ material. However, there is a slight discrepancy between the acceptor density determined by the Hall effect and Mott-Schottky measurements that could be attributed to sensitivity to surface effects, sample homogeneity, and band bending. The derived $V_{\rm fb}$ of the bare and irradiated Sb₂S₃ films at 5, 10, 15, and 20 kGy were 0.31, 0.29, 0.27, 0.17, and 0.24 V vs. RHE, respectively. It was gradually decreased along with the increased irradiation doses up to 15 kGy, while it was increased around the value of 0.24 V vs. RHE for the irradiation dose of 20 kGy. In other words, the band bending at the photocathode/electrolyte interface is strengthened by increasing the irradiation doses up to 15 kGy, while it decreases when the irradiation doses reach 20 kGy. By the way, the Mott-Schottky curve exhibits nonlinearity in the potential range from -0.2 to 0.4 V vs. RHE. This behavior could be attributed to various factors related to the Sb₂S₃/Na₂SO₄ interface, such as interface roughness and/or surface states at the Sb₂S₃ samples. 80 The downward shift of the V_{fb} value toward the valence band indicates a decrease in the Fermi level, leading to an increase in the hole concentration of the Sb2S3 photocathode. Based on these results, the optimized photocathode (15 kGy irradiated film) enables more efficient electron transfer between the Sb₂S₃/Na₂SO₄ interface. Thus, the higher photocurrent revealed by the optimized photocathode could be explained by the high concentration and separation efficiency of the photogenerated species, resulting in improved PEC performance. Fig. 17 illustrates the mechanism of the PEC process, wherein photogenerated species encounter water molecules in the electrolyte after absorbing a photon. The electrons traverse through the conduction band of the working electrode and directly react with two protons in the Na2SO4 buffer electrolyte

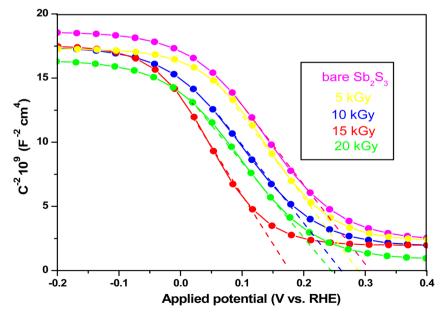


Fig. 16 Mott–Schottky plots of bare and irradiated Sb₂S₃-based photocathodes.

Paper RSC Advances

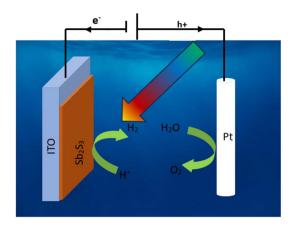


Fig. 17 Schematic mechanism of photoelectrochemical water splitting of ${\rm Sb_2S_3\text{-}based}$ photocathode.

to produce H_2 , while the holes traverse through the external wire circuit until they reach the Pt electrode. There, they react with two H_2O molecules to generate O_2 . The primary event that induces the observed photocurrents is likely water reduction to H_2 gas. To quantify the amount of H_2 in the gas phase, H_2 evolution across all Sb_2S_3 photocathodes was measured via micro gas chromatography (GC) using a gas-tight syringe as the delivery tool. Fig. 18 exhibits the amount of H_2 evolved from a unit area of all Sb_2S_3 photocathodes versus time under standard one sun (100 mW cm $^{-2}$) illumination at 0 V vs. RHE. We have not included the error bar here since each calculated gas evolution rate is the measurement of 2–3 GC tests. We have used the average PPM (parts per million) to estimate the rate of hydrogen evolution. It is worth noting that the linear

relationship shows the excellent stability of the synthesized samples. On the other hand, the bare sample displays poor hydrogen evolution activity of around 2.07 $\mu mol\ h^{-1}$ owing to the limited light absorption, which was in good agreement with the previous literature reports.81 According to Xiao et al.82 this phenomenon could be explained by the effect of overvoltage for the hydrogen evolution activity, which requests the bandgap value of the semiconductor material to be over 1.8 eV, while that of bare Sb₂S₃ was only 1.78 eV. However, the hydrogen evolution activity of irradiated samples increased, demonstrating that the irradiated Sb₂S₃ samples perform efficient photocatalytic reactions under visible light. The evolution rate of H2 increases with increasing γ radiation doses and attains a maximum of 17.20 μ mol h⁻¹ at 15 kGy, which is about 8.3 times higher than that of the bare sample. Thereafter, further increasing the γ radiation doses led to a significant reduction in photoactivity, which is evident from the lower H₂ evolution rate of the 20 kGy sample (9.7 μ mol h⁻¹). To establish the total volume of hydrogen gas produced during 180 minutes of the best optimized films, the FE was determined through a comparative analysis of the detected volume of H2 gas and the calculated volumes of H2 gas with a theoretical 100% FE, as shown in the inset of Fig. 18. During about 180 minutes, 9.0 mL of H2 with an FE of nearly 95.36% was achieved. The remaining 4.64% could be due to ineffective gas collection and/or some parasitic electrochemical processes. Such a phenomenon has also been demonstrated in another PEC water-splitting system.83 We have conclusively demonstrated that the 15 kGy photocathode is highly effective for PEC water splitting to produce H2 gas. However, ongoing efforts are focused on further improving the quality of the Sb₂S₃ semiconductor and optimizing processes for surface adjustments.

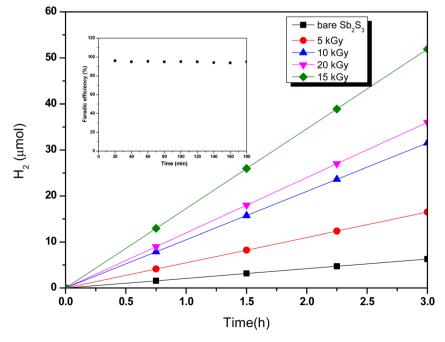


Fig. 18 Hydrogen evolution as a function of time for different Sb_2S_3 -based photocathodes under standard one sun (100 mW cm⁻²) illumination at 0 V vs. RHE. The inset plot of Fig. 15 stands for the faradaic efficiency (FE) measurement of the optimized Sb_2S_3 -based photocathode (15 kGy).

4. Conclusions

In summary, the introduction of sulfur vacancies into Sb₂S₃ thin films through γ -irradiation was carried out to enhance its PEC performance for hydrogen production. γ-irradiation led to an improved crystal structure, reduction in the band gap energy, and altered morphology of Sb₂S₃ film, resulting in suppressed recombination of photogenerated carriers and enhanced charge transportation. Moreover, the irradiation process produced an increase in Sb₂S₃ film conductivity. The PEC water-splitting analysis discloses that the film treated under an irradiated dose of 15 KGy photocathode boosted the photocurrent density from 0.60 mA cm $^{-2}$ to 1.62 mA cm $^{-2}$ at 0 V ν s. RHE (2.7-fold enhancement) compared with bare Sb₂S₃. The significant enhancement in PEC performance is attributed to various factors, including crystallite size, surface roughness, low wettability, and band gap. Hence, γ-irradiation offers a novel strategy for controlling the surface vacancies of Sb₂S₃ films, leading to high PEC performance. The treatment with γ -irradiation showed outstanding performance in photo-generated charge transfer and separation. Our outstanding results open a new avenue that highlights the energetic influence of γ -irradiation on Sb₂S₃ thin films and enables the construction of highly stable and efficient photocathodes for solar-driven PEC water-splitting applications.

Conflicts of interest

The author confirms that there are no known competing financial interests or personal relationships associated with this publication for this work that could have influenced its outcome.

Acknowledgements

I enthusiastically acknowledge financial support from the Center of Research and Technology of Energy, Technopole of Borj Cedria, Tunisia.

References

- 1 A. J. Hasan and S. A. Rasheed, Evaluating the Performance and Exhaust Emissions of a Micro Gas Turbine Engine Fueled by Kerosene and Olive Oil Methyl Ester Blends, *Int. J. Heat Technol.*, 2023, **41**(4), 1063–1073.
- 2 J. Guo, Y. Zhang, A. Zavabeti, K. Chen, Y. Guo, G. Hu, X. Fan and G. K. Li, Hydrogen production from the air, *Nat. Commun.*, 2022, **13**, 5046.
- 3 S. Wang, A. Lu and C. J. Zhong, Hydrogen production from water electrolysis: role of catalysts, *Nano Convergence*, 2021, **8**, 4.
- 4 M. M. Rampai, C. B. Mtshali, N. S. Seroka and L. Khotseng, Hydrogen production, storage, and transportation: recent advances, *RSC Adv.*, 2024, **14**, 6699–6718.
- 5 E. Park, J. Yoo and K. Lee, Enhanced photoelectrochemical hydrogen production via linked BiVO₄ nanoparticles on

- anodic WO₃ nanocoral structures, *Sustainable Energy Fuels*, 2024, **8**, 1448–1456.
- 6 M. Ali, E. Pervaiz, U. Sikandar and Y. Khan, A review on the recent developments in zirconium and carbon-based catalysts for photoelectrochemical water-splitting, *Int. J. Hydrogen Energy*, 2021, **46**, 18257–18283.
- 7 Z. Wang, J. Fan, B. Cheng, J. Yu and J. Xu, Nickel-based cocatalysts for photocatalysis: hydrogen evolution, overall water splitting, and CO₂ reduction, *Mater. Today Phys.*, 2020, 15, 100279.
- 8 Z. Xu, Z. Guan, J. Yang and Q. Li, Band Positions and Photoelectrochemical Properties of Solution-Processed Silver-Substituted Cu₂ZnSnS₄ Photocathode, *Appl. Energy Mater.*, 2019, **2**, 2779–2785.
- 9 A. C. Salomao, M. dos Santos Araujo, H. L. S. dos Santos, M. Medina, L. H. Mascaro and M. A. S. Andrade Junior, Towards Highly Efficient Chalcopyrite Photocathodes for Water Splitting: The Use of Cocatalysts beyond Pt, ChemSusChem, 2021, 14(21), 4671-46794.
- 10 J. Lia, M. Griep, Y. Choib and D. Chu, Photoelectrochemical overall water splitting with textured CuBi₂O₄ as a photocathode, *Chem. Commun.*, 2018, 54(27), 3331–3334.
- 11 M. B. Akbar, Y. Wang, X. Zhang and T. He, Study on photoelectrochemical CO₂ reduction over Cu₂O, *J. Photochem. Photobiol.*, *A*, 2023, 4371, 114483.
- 12 W. Yang, J. H. Kim, O. S. Hutter, L. J. Phillips, J. Tan, J. Park, H. Lee, J. D. Major, J. S. Lee and J. Moon, Benchmark Performance of Low-Cost Sb₂Se₃ Photocathodes for Unassisted Solar Overall Water Splitting, *Nat. Commun.*, 2020, **11**, 861.
- 13 J. A. Christians, D. T. L. Jr. and P. V. Kamat, Rate limiting interfacial hole transfer in Sb₂S₃ solid-state solar cells, *Energy Environ. Sci.*, 2014, 7, 1148–1158.
- 14 W. Zhang, M. Tan, P. Zhang, L. N. Zhang, W. N. Dong, Q. S. Wang, J. W. Ma, E. L. Dong, S. C. Xu and G. Q. Wang, one pot synthesis of Sb₂S₃ nanocrystalline films through a PVP-assisted hydrothermal process, *Appl. Surf. Sci.*, 2018, 455, 1063–1069.
- 15 J. C. Cardoso, C. A. Grimes, X. J. Feng, X. Zhang, S. Komarneni, M. V. Zanoni and N. Bao, Fabrication of Coaxial TiO₂/Sb₂S₃ Nanowire Hybrids for Efficient Nanostructured Organic-inorganic Thin Film Photovoltaics, *Chem. Commun.*, 2012, **48**, 2818–2820.
- 16 L. J. Phillips, C. N. Savory, O. S. Hutter, P. J. Yates, H. Shiel, S. Mariotti, L. Bowen, M. Birkett, K. Durose, D. O. Scanlon and J. D. Major, Current Enhancement via a TiO₂ Window Layer for CSS Sb₂Se₃ Solar Cells: Performance Limits and High V_{OC}, *IEEE J. Photovolt.*, 2019, 9(2), 544–551.
- 17 M. A. Farhana, A. Manjceevan and J. Bandara, Recent advances and new research trends in Sb₂S₃ thin film based solar cells, *J. Sci. Adv. Mater. Dev.*, 2023, **8**, 100533.
- 18 Y. C. Choi, D. U. Lee, J. H. Noh, E. K. Kim and S. I. I. Seok, highly improved Sb_2S_3 sensitized-inorganic-organic heterojunction solar cells and quantification of traps by deep-level transient spectroscopy, *Adv. Funct. Mater.*, 2014, 24, 3587–3592.

Paper

19 N. Spalatu, J. Hiie, R. Kaupmees, O. Volobujeva, J. Krustok, I. O. Acik and M. Krunks, Postdeposition processing of SnS thin films and solar cells: prospective strategy to obtain large, sintered, and doped SnS grains by recrystallization in the presence of a metal halide flux, *ACS Appl. Mater. Interfaces*, 2019, **11**, 17539–17554.

- 20 R. R. Prabhakar, T. Moehl, S. Siol, J. Suh and S. David Tilley, Sb₂S₃/TiO₂ Heterojunction Photocathodes: Band Alignment and Water Splitting Properties, *Chem. Mater.*, 2020, 32(17), 7247–7253.
- 21 P. Ge, H. Hou, X. Ji, Z. Huang, S. Li and L. Huang, Enhanced stability of sodium storage exhibited by carbon-coated Sb₂S₃ hollow spheres, *Mater. Chem. Phys.*, 2018, **203**(1), 185–192.
- 22 A. Chihi, Effect of Ruthenium doping in tailoring structure, optical and electrical properties of Sb₂S₃ thin film synthesized via electrodeposition technique, *J. Mater. Sci.: Mater. Electron.*, 2023, 34, 2087.
- 23 Q. Cai, Z. Liu, C. Han, Z. Tong and C. Ma, CuInS₂/Sb₂S₃ heterostructure modified with noble metal co-catalyst for efficient photoelectrochemical water splitting, *J. Alloys Compd.*, 2019, **795**, 319–326.
- 24 A. Chihi, Effect of gamma radiations on the physical and photoelectrochemical properties of CuSbS₂ thin films prepared via spin coating technique, *J. Electron. Mater.*, 2023, **52**, 6749–6759.
- 25 J. Alarcon, S. Ponce, F. Paraguay-Delgado and J. Rodriguez, Effect of Gamma- Irradiation on the Growth of ZnO Nanorod Films for Photocatalytic Disinfection of Contaminated Water, J. Colloid Interface Sci., 2011, 364, 49–55.
- 26 M. Mohil and G. A. Kumar, Gamma Radiation Induced Effects in TeO₂ Thin Films, *J. Nano- Electron. Phys.*, 2013, 5, 5–7.
- 27 S. Wang, P. Li, L. Sheng, L. Song, R. Zang, S. Liu, L. Liu and W. Zhou, Regulating the surface state of ZnIn₂S₄ by gammaray irradiation for enhanced photocatalytic hydrogen evolution, *Catal. Sci. Technol.*, 2022, **12**, 927–934.
- 28 N. A. Mohamed, H. Ullah, J. Safaei, A. F. Ismail, M. F. M. Noh, M. F. Soh, M. A. Ibrahim, N. A. Ludin and M. A. M. Teridi, Efficient Photoelectrochemical Performance of Gamma Irradiated g-C₃N₄ and its g-C₃N₄@BiVO₄ Heterojunction for Solar Water Splitting, *J. Phys. Chem. C*, 2019, **123**(14), 9013–9026.
- 29 T. Han, M. Luo, Y. Liu, C. Lu, Y. Ge, X. Xue, W. Dong, Y. Huang, Y. Zhou and X. Xu, Sb₂S₃/Sb₂Se₃ heterojunction for high-performance photodetection and hydrogen production, *J. Colloid Interface Sci.*, 2022, **628**, 886–895.
- 30 Z. Wang, L. Li, L. Hong, X. Shi, Y. Lu and J. Su, Bi-Doped Sb₂S₃ Thin Film Synthesized by a Two-Step Approach with Enhanced Photoelectrochemical Water Splitting Performance, *J. Electrochem. Soc.*, 2022, **169**, 066508.
- 31 X. Liu, L. Zhang, W. Jin, Q. Li, Q. Sun, Y. Wang, E. Liu, X. Hu and H. Miao, Epitaxial growth strategy for construction of Tm³⁺ doped and [hk1] oriented Sb₂S₃ nanorods S-scheme heterojunction with enhanced photoelectrochemical performance, *Chem. Eng. J.*, 2023, 475, 146315.

- 32 V. Sharma, T. K. Das, P. Ilaiyaraja, A. C. Dakshinamurthy and C. Sudakar, Growth of Sb₂S₃ semiconductor thin film on different morphologies of TiO₂ nanostructures, *Mater. Res. Bull.*, 2020, **131**, 110980.
- 33 A. D. DeAngelis, K. C. Kemp, N. Gaillard and K. S. Kim, Antimony (III) Sulfide Thin Films as a Photoanode Material in Photocatalytic Water Splitting, ACS Appl. Mater. Interfaces, 2016, 8(13), 8445–8451.
- 34 Q. Han, S. Sun, D. Sun, J. Zhu and X. Wang, Room-temperature synthesis from molecular precursors and photocatalytic activities of ultralong Sb₂S₃nanowires, *RSC Adv.*, 2011, **1**, 1364–1369, DOI: **10.1039/C1RA00379H.**
- 35 C. D. Wagner, A. V. Naumkin, A. Kraut-Vass, J. W. Allison, C. J. Powell and J. R. Rumble Jr., NIST Standard Reference Database 20, Version 3.4, National Institute of Standards and Technology, Gaithersburg, 2003.
- 36 D. Necas and P. Klapetek, Cent. Eur. J. Phys., 2012, 10, 181– 188.
- 37 D. Craciun, G. Socol, S. L. Caër, L. M. Trinca, A. C. Galca, D. Pantelica, P. Ionescu and V. Craciun, Gamma irradiation effects on the properties of indium zinc oxide thin films, *Thin Solid Films*, 2016, 614, 2–6.
- 38 T. Stamenkovi, N. Bundaleski, T. Barudzija, I. Validzi and V. Lojpur, XPS study of iodine and tin doped Sb₂S₃ nanostructures affected by non-uniform charging, *Appl. Surf. Sci.*, 2021, **567**, 150822.
- 39 R. Basu, S. Mandava, U. S. Shenoy, D. K. Bhat, B. Khasimsaheb, A. K. Debnath, A. Singh and S. Neeleshwar, Synergistic manifestation of band and scattering engineering in the single aliovalent Sb alloyed anharmonic SnTe alloy in concurrence with rule of parsimony, *Mater. Adv.*, 2021, 2, 7891–7906.
- 40 S. Oswald and W. Bruckner, XPS Depth Profile Analysis of Non-Stoichiometric NiO Films, *Surf. Interface Anal.*, 2004, **36**, 17–22.
- 41 J. F. Felix, A. F. da Silva, S. W. da Silva, F. Qu, B. Qiu, J. Ren, W. M. de Azevedo, M. Heninid and C. C. Huang, A comprehensive study on the effects of gamma radiation on the physical properties of a two-dimensional WS₂ monolayer semiconductor, *Nanoscale Horiz.*, 2020, 5, 259–267.
- 42 O. E. L. Pérez, M. D. Sánchez and M. L. Teijelo, Characterization of growth of anodic antimony oxide films by ellipsometry and XPS, *J. Electroanal. Chem.*, 2010, 645, 143–148.
- 43 A. Kumar, P. Kumar, M. R. Tripathy, A. K. Arora and R. P. Tandon, Effect of γ -irradiation on oxygen content and kinetic parameters of high Tc Y₁Ba₂Cu₃O_{7- δ} superconductors, *Mater. Chem. Phys.*, 2006, **97**(2-3), 230–235.
- 44 B.-R. Chen, S. Lany, L. L. Kelly, E. Arca, Y. Iguchi, J. D. Perkins, H. Yanagi, M. F. Toney, L. T. Schelhas and A. Zakutayev, Antimony nitride discovered by theoretical structure prediction, rapid thermal annealing, and in situ X-ray diffraction, *Cell Rep. Phys. Sci.*, 2022, 3(8), 100980.
- 45 M. Deng, S. Li, W. Hong, Y. Jiang, W. Xu, H. Shuai, H. Li, W. Wang, H. Hou and X. Ji, Natural stibnite ore (Sb₂S₃)

- embedded in sulfur-doped carbon sheets: enhanced electrochemical properties as anode for sodium ions storage, *RSC Adv.*, 2019, **9**, 15210–15216.
- 46 D. Gupta, V. Chauhan, A. Mahajan, R. Gupta, S. Asad Ali and R. Kumar, Influence of gamma radiation on optical, structural and surface morphological properties of WO₃ thin films grown by RF sputtering, *Radiat. Phys. Chem.*, 2023, 202, 110554.
- 47 C. L. Tracy, J. McLain Pray, M. Lang, D. Popov, C. Park and C. Trautmann, Defect accumulation in ThO₂ irradiated with swift heavy ions, *Nucl. Instrum. Methods Phys. Res.*, *Sect. B*, 2014, **326**, 169–173.
- 48 M. Souli, C. Nefzia, Z. Sebouia, A. Mejri, R. Viduc and N. Kamoun-Turki, improved structural properties, morphological and optical behaviors of sprayed Cu₂ZnSnS₄ thin films induced by high gamma radiations for solar cells, *Mater. Sci. Semicond. Process.*, 2018, **83**, 50–57.
- 49 L. Li, J. Li, B.-H. Kim and J. Huang, The effect of morphology and crystal structure on the photocatalytic and photoelectrochemical performances of WO₃, RSC Adv., 2024, **14**, 2080–2087.
- 50 M. El-Hagary, M. Emam-Ismail, E. R. Shaaban and A. El-Taher, Effect of γ -irradiation exposure on optical properties of chalcogenide glasses $Se_{70}S_{30-x}Sb_x$ thin films, *Radiat. Phys. Chem.*, 2012, **81**(10), 1572–1577.
- 51 Q. Wang, F. Liu, L. Wang, L. Jiang, Q. Wang, B. Hong and Y. Lai, towards fast and low cost Sb₂S₃ anode preparation: a simple vapor transport deposition process by directly using antimony sulfide ore as raw material, *Scr. Mater.*, 2019, 173, 75–79.
- 52 E. M. Mkawi, Solvothermal orthorhombic Sb₂S₃ nanobars: effect of hydrothermal temperature in properties for solar cell application, *Results Phys.*, 2020, **19**, 103603.
- 53 Y. Xie, K. Li, X. Li, F. Gao, X. Xiong, G. Zeng and B. Li, Fabrication of Sb₂S₃ solar cells by close space sublimation and enhancing the efficiency via co-selenization, *Mater. Sci. Semicond. Process.*, 2022, **142**, 106451.
- 54 V. Sharma, P. Ilaiyaraja, A. C. Dakshinamurthy and C. Sudakar, One step thermolysis of Sb-Mercaptopropionic acid complex in ambient air atmosphere for growing Sb₂S₃ thin films with controlled microstructure, *Mater. Sci. Semicond. Process.*, 2021, **121**, 105330.
- 55 H. Ning, H. Guo, J. Zhang, X. Wang, X. Jia, J. Qiu, N. Yuan and J. Ding, Enhancing the efficiency of Sb₂S₃ solar cells using dual-functional potassium doping, *Sol. Energy Mater. Sol. Cells*, 2021, 221, 110816.
- 56 A. Chihi, Structure and Optical Properties of Cu (In_{0.7}, Ga_{0.3}) Se₂ Absorbers on Copper Substrate for Photovoltaic Solar Cells Application, *Optik*, 2016, 127(23), 11469–11478.
- 57 A. Chihi, Impact of Ag-coating on CAS thin film for boosted photoelectrochemical water splitting, *Appl. Phys. A*, 2023, 129, 472.
- 58 S. Rahman and S. R. Al Ahmed, Photovoltaic performance enhancement in CdTe thin-film heterojunction solar cell with Sb_2S_3 as hole transport layer, *Sol. Energy*, 2021, 230, 605–617.

- 59 R. A. Ismail, N. F. Abeduljabbar and M. W. Fatehi, Effect of dipping time on the properties of Sb₂S₃/Si heterojunction prepared by chemical bath deposition, *Mater. Res. Express*, 2019, **6**, 045915.
- 60 K. Y. Rajpure and C. H. Bhosale, Preparation and characterization of spray deposited photoactive Sb₂S₃ and Sb₂Se₃ thin films using aqueous and non-aqueous media, *Mater. Chem. Phys.*, 2002, 73, 6–12.
- 61 D. L. M. Cordova, K. Chua, R. M. Huynh, T. Aoki and M. Q. Arguilla, Anisotropy-Driven Crystallization of Dimensionally Resolved Quasi-1D Van der Waals Nanostructures, *J. Am. Chem. Soc.*, 2023, **145**, 41.
- 62 Z. Peng, Q. Zheng, R. Wang, L. Sun, H. Wang, Y. Yuan, Y. Xing, L. Yao, J. Bi and W. Li, Controllable (h k 1) preferred orientation of Sb₂S₃ thin films fabricated by pulse electrodeposition, *Sol. Energy Mater. Sol. Cells*, 2023, 253, 112208.
- 63 R. Vadapoo, S. Krishnan, H. Yilmaz and C. Marin, Self-standing nanoribbons of antimony selenide and antimony sulfide with well-defined size and band gap, *Nanotechnology*, 2011, 22, 175705.
- 64 B. R. Bricchi, M. Sygletou, L. Ornago, G. Terraneo, d. F. Bisio, C. Mancarella, L. Stasi, F. Rusconi, E. Mogni, M. Ghidelli, P. Biagioni and A. L. Bass, Optical and electronic properties of transparent conducting Ta: TiO₂ thin and ultra-thin films: the effect of doping and thickness, *Mater. Adv.*, 2021, 2, 7064–7076.
- 65 N. A. Mohamed, A. F. Ismail, J. Safaei and M. A. M. Teridi, Gamma irradiation-induced elemental O/N co-doping and structural reinforcement in g-C₃N₄ photo-electrocatalyst, *Appl. Surf. Sci.*, 2023, **616**, 156615.
- 66 Z. Li, S. Fang, H. Sun, R.-J. Chung, X. Fang and J.-H. He, Solar Hydrogen, *Adv. Energy Mater.*, 2023, **13**(8), 2203019.
- 67 A. N. Kulkarni, S. A. Arote, H. M. Pathan and R. S. Patil, Room temperature synthesis of crystalline Sb₂S₃ for SnO₂ photoanode-based solar cell application, *Bull. Mater. Sci.*, 2015, **38**, 493–498.
- 68 R. Krautmann, N. Spalatu, R. Josepson, R. Nedzinskas, R. Kondrotas, R. Gržibovskis, A. Vembris, M. Krunks and I. O. Acik, Low processing temperatures explored in Sb₂S₃ solar cells by close-spaced sublimation and analysis of bulk and interface related defects, Sol. Energy Mater. Sol. Cells, 2023, 251, 112139.
- 69 E. Aslan and M. Zarbali, Preparation of high-performance Sb₂S₃ based visible-light photodetector with excellent reversibility, *Opt. Mater.*, 2022, **133**, 113028.
- 70 S. A. Mahadik, R. G. Sonkawade, F. Pedraza, L. B. Phadatare, A. K. Bhagate and M. R. Waikar, Enhancing photoelectrochemical performance through surface engineering of CdSe and Al-doped CdSe nanoparticles on ZnO/FTO photoanodes, *Int. J. Hydrogen Energy*, 2024, 51, 676–689.
- 71 M. A. de Araújo and L. H. Mascaro, Plasma Treatment: a Novel Approach to Improve the Photoelectroactivity of Sb_2S_3 Thin Films to Water Splitting, *ChemElectroChem*, 2020, 7, 2325–2329.

- 72 J. D. Musgraves, J. Hu and L. Calvez, *Springer Handbook of Glass*, Springer, Switzerland, 2019, p. 1599.
- 73 M. G. Kast, L. J. Enman, N. J. Gurnon, A. Nadarajah and S. W. Boettcher, Solution-Deposited F: SnO₂/TiO₂ as a Base-Stable Protective Layer and Antireflective Coating for Microtextured Buried-Junction H₂-evolving Si Photocathodes, ACS Appl. Mater. Interfaces, 2014, 6(24), 22830–22837.
- 74 L. Pan, Y. Liu, L. Yao, R. Dan, K. Sivula, M. Grätzel and A. Hagfeldt, Cu₂O photocathodes with band-tail states assisted hole transport for standalone solar water splitting, *Nat. Commun.*, 2020, 11, 318.
- 75 R. R. Prabhakar, T. Moehl, S. Siol, J. Suh and S. D. Tilley, Sb₂S₃/TiO₂ Heterojunction Photocathodes: Band Alignment and Water Splitting Properties, *Chem. Mater.*, 2020, 32(17), 7247–7253.
- 76 Z. He, Y. Wang, X. Dong, N. Zheng and X. Zhang, Indium sulfide nanotubes with sulfur vacancies as an efficient photocatalyst for nitrogen fixation, *RSC Adv.*, 2019, 9, 21646–21652.
- 77 S. Bai, S. Jia, S. Yan, Y. Zhao, P. Tang, R. Luo, Y. Feng, D. Li and A. Chen, Facile synthesis of Bi NPs modified BiVO₄/ ZnFe₂O₄ heterojunction for PEC water splitting, *Int. J. Hydrogen Energy*, 2024, 54, 1008–1016.
- 78 X. Liu, Z. Cai, L. Wan, P. Xiao, B. Che, J. Yang, H. Niu, H. Wang, J. Zhu, Y.-T. Huang, H. Zhu, S. J. Zelewski, T. Chen, R. L. Z. Hoye and R. Zhou, Grain Engineering of

- Sb_2S_3 Thin Films to Enable Efficient Planar Solar Cells with High Open-Circuit Voltage, *Adv. Mater.*, 2023, 36(1), e2305841.
- 79 F. Mohamadkhani, M. Heidariramsheh, S. Javadpour, E. Ghavaminia, S. M. Mahdavi and N. Taghavinia, Sb₂S₃ and Cu₃SbS₄ nanocrystals as inorganic hole transporting materials in perovskite solar cells, *Sol. Energy*, 2021, 223, 106–112.
- 80 A. Song, S. P. Berglund, A. Chemseddine, D. Friedrich, F. F. Abdi and R. van de Krol, Elucidating the optical, electronic, and photoelectrochemical properties of p-type copper vanadate (p-Cu₅V₂O₁₀) photocathodes, *J. Mater. Chem. A*, 2020, 8, 12538.
- 81 N. Son, J. Y. Do and M. Kang, Characterization of core@shell-structured ZnO@Sb₂S₃ particles for effective hydrogen production from water photo spitting, *Ceram. Int.*, 2017, 43, 11250–11259.
- 82 Y. Xiao, H. Wangb, Y. Jiang, W. Zhang, J. Zhang, X. Wu, Z. Liu and W. Deng, Hierarchical Sb₂S₃/ZnIn₂S₄ core–shell heterostructure for highly efficient photocatalytic hydrogen production and pollutant degradation, *J. Colloid Interface Sci.*, 2022, **623**, 109–123.
- 83 Y. Kawai, K. Nagai and T. Abe, A visible-light-induced photoelectrochemical water-splitting system featuring an organo-photocathode along with a tungsten oxide photoanode, *RSC Adv.*, 2017, 7, 34694–34698.