







Cu-based S-scheme photocatalysts

Cite this: DOI: 10.1039/d4cs01091d

 Mahmoud Sayed, ^{ad} Kezhen Qi,^b Xinhe Wu,^{*a} Liuyang Zhang, ^a
 Hermenegildo García ^{*c} and Jiaguo Yu ^{*a}

S-scheme heterojunctions have become a hot topic in photocatalysis. Copper (Cu) compounds are a versatile family of photocatalytic materials, including oxides (CuO, Cu₂O), binary oxides (CuBi₂O₄, CuFe₂O₄), sulfides (Cu_xS, (1 ≤ x ≤ 2)), selenides (CuSe), phosphides (Cu₃P), metal organic frameworks (MOFs), etc. These materials are characterized by narrow bandgaps, large absorption coefficients, and suitable band positions. To further increase the efficiency of photoinduced charge separation, Cu-based photocatalytic materials are widely integrated into S-scheme heterojunctions and exploited for the hydrogen evolution reaction (HER), CO₂ reduction, H₂O₂ generation, N₂ fixation, and pollutant degradation. This review comprehensively discusses recent progress in Cu-based S-scheme heterojunctions, and highlights their considerable potential for targeted applications in sustainable energy conversion, environmental remediation, and beyond. The fundamentals of S-scheme charge transfer, the design principles and verification tools are summarized. Then, the review describes the Cu-based photocatalytic materials, categorized according to their chemical composition, and their integration in S-scheme heterojunctions for photocatalytic applications. In particular, the implications of the S-scheme charge transfer mechanism on promoting the catalytic activity of selected systems are analyzed. Finally, current limitations and outlooks are provided to motivate future studies on developing novel and advanced Cu-based S-scheme photocatalysts with high performance and studying the underlying photocatalytic mechanisms.

Received 17th December 2024

DOI: 10.1039/d4cs01091d

rsc.li/chem-soc-rev

^a *Laboratory of Solar Fuel, Faculty of Materials Science and Chemistry, China University of Geosciences, 68 Jincheng Road, Wuhan 430078, P. R. China.*

E-mail: wuxinhe@hbnu.edu.cn, yujiaguo93@cug.edu.cn

^b *College of Pharmacy, Dali University, Dali 671003, P. R. China*

^c *Department of Chemistry, Universitat Politècnica de València, 46022 Valencia, Spain. E-mail: hgarcia@gim.upv.es*

^d *Chemistry department, Faculty of Science, Fayoum University, Fayoum 63514, Egypt*

1. Introduction

Photocatalysis has emerged as a green technology for sustainable energy conversion and environmental remediation applications. Its unique feature of converting inexhaustible solar energy into chemical fuels in a renewable and readily applicable manner endows photocatalysis with considerable potential


Mahmoud Sayed

Mahmoud Sayed received his BSc (2012) and MSc (2017) in chemistry from Fayoum University, Egypt, and PhD from Wuhan University of Technology, China, under the supervision of Prof. Jiaguo Yu. Currently, he is a postdoctoral fellow in Prof. Jiaguo Yu's group at the Laboratory of Solar Fuel, China University of Geosciences, Wuhan, China. His research interest focuses on the design and integration of photocatalytic materials in energy conversion and environmental applications.


Kezhen Qi

Kezhen Qi received his BS and MS degrees in physics from Shenyang Normal University and his PhD in material physics and chemistry in 2013 from Nankai University. During 2014–2015, he worked as a postdoc in Prof. Wojciech Macyk's group, at Jagiellonian University, Poland. Now, he works at Dali University as a professor and his research interests include the synthesis of nanomaterials, and their applications in environmental chemistry and energy conversion, with a particular focus on photocatalysis.



for green energy production in this era. It also provides a straightforward approach for effective environmental pollutant mineralization.^{1,2} Different photocatalytic materials, such as TiO₂, ZnO, Cu₂O, g-C₃N₄, CdS, and MOFs, have been tested for a wide range of applications including pollutant degradation, H₂ evolution, CO₂ reduction, H₂O₂ production, and organic transformations.^{3–6} However, the efficiency of a single photocatalytic material is still limited by the high electron–hole recombination rate, diminished light absorption ability, and the absence of a driving force for preferential charge mobility and transport (Fig. 1). To resolve these challenges, it is reasonable to introduce photo-based processes that occur when incident light impinges the catalyst surface. After the semiconductor is irradiated with light, the light portion has a shorter wavelength than the material absorption onset can be absorbed. The absorbed

light can induce electronic excitation from the valence band (VB) to the conduction band (CB) (path 1 in Fig. 1a). This electron promotion leaves behind a hole in the VB. Due to the strong Coulombic attraction between the photogenerated geminal electron and hole, the majority of these charge carriers tend to recombine. Alternatively, they can also annihilate after random diffusion within the bulk of the photocatalyst (path 2 in Fig. 1a). For a single photocatalytic component, there is almost no driving force to steer the charge transfer to the catalyst surface. If the charge carriers reach the surface, they can undergo recombination at surface defects and/or impurities acting as recombination centers (path 3 in Fig. 1a). The electrons and holes that still survived at the surface can participate in reduction and oxidation reactions, respectively (path 4 in Fig. 1a). The CB and VB energy levels determine the reduction



Xinhe Wu

Xinhe Wu received his BS and MS degrees in chemistry from the Hubei Normal University and Wuhan University of Technology, respectively, and his PhD degree in materials science and engineering in 2021 from Wuhan University of Technology. In 2021, he became a lecturer at the Hubei Normal University. In 2023, he became an associate professor at the Hubei Normal University. Furthermore, he was selected into the Chutian Scholars Talent Program of Hubei Province. His scientific interests include semiconductor photocatalysis such as photocatalytic hydrogen and hydrogen peroxide production, CO₂ reduction to hydrocarbon fuels, and antibiotics degradation.



Liuyang Zhang

Liuyang Zhang received her Bachelor of Science degree (2012) from Shanghai Jiao Tong University. Subsequently, she received her PhD degree in materials science and engineering from the National University of Singapore (NUS) in 2016. She worked as a research fellow at NUS before joining the State Key Laboratory of Advanced Technology for Materials Synthesis and Processing at Wuhan University of Technology as an associate professor in August 2017. She has been a professor at the China University of Geosciences since November 2021. Her main research background lies in the areas of photocatalysis and electrochemical energy storage.



Hermenegildo Garcia

Prof. H. Garcia is a Professor at the Technical University of Valencia and a member of the Institute of Chemical Technology of the Spanish National Research Council. He has published over 900 research articles and has a personal H-index of 136 (Google Scholar) and 122 (Web of Science) with over 70 000 citations. He has been a continuously Highly Cited Researcher for ten consecutive years since this list was first issued by the Shanghai Jiao Tong University in 2013 and then by Clarivate. The number of publications with over 100 citations is 186.

Prof. H. Garcia is a Professor at the Technical University of Valencia and a member of the Institute of Chemical Technology of the Spanish National Research Council. He has published over 900 research articles and has a personal H-index of 136 (Google Scholar) and 122 (Web of Science) with over 70 000 citations. He has been a continuously Highly Cited Researcher for ten consecutive years since this list was first issued by the Shanghai Jiao Tong University in 2013 and then by Clarivate. The number of publications with over 100 citations is 186.



Jianguo Yu

Prof. Jianguo Yu received his BS and MS in chemistry from the Central China Normal University and Xi'an Jiaotong University, respectively, and PhD in materials science from the Wuhan University of Technology (WUT). His research interests include semiconductor photocatalysis, photocatalytic hydrogen production, CO₂ reduction, perovskite solar cells, and electrocatalysis. He is a Foreign Member of Academia Europaea (2020) and a Foreign Fellow of the European Academy of Sciences (2020). He obtained the 35th Khwarizmi International Award (2022). His name was also on the list of Highly Cited Researchers from Clarivate Analytics (previously Thomson Reuters) in chemistry, materials science, and engineering from 2014–2023.

Prof. Jianguo Yu received his BS and MS in chemistry from the Central China Normal University and Xi'an Jiaotong University, respectively, and PhD in materials science from the Wuhan University of Technology (WUT). His research interests include semiconductor photocatalysis, photocatalytic hydrogen production, CO₂ reduction, perovskite solar cells, and electrocatalysis. He is a Foreign Member of Academia Europaea (2020) and a Foreign Fellow of the European Academy of Sciences (2020). He obtained the 35th Khwarizmi International Award (2022). His name was also on the list of Highly Cited Researchers from Clarivate Analytics (previously Thomson Reuters) in chemistry, materials science, and engineering from 2014–2023.



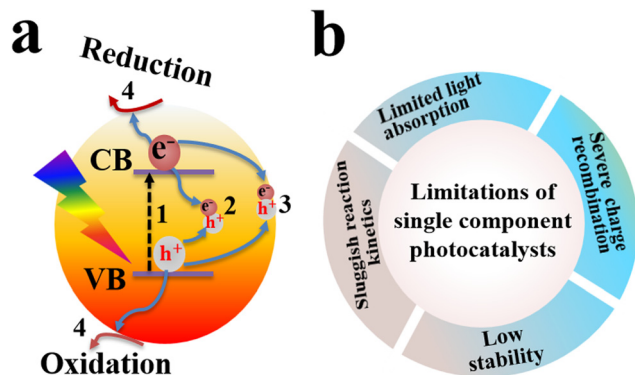


Fig. 1 (a) Schematic illustration of photo-based processes that occur after light absorption by a semiconductor. Paths 1–4 represent electron excitation from the VB to the CB leaving behind a hole at the VB, electron–hole recombination within the bulk, electron–hole recombination at the surface, and consumption of separated electrons and holes in the surface reactions, respectively. (b) Limitations of single component photocatalysts.

and oxidation potential of photogenerated electrons and holes within a semiconductor, respectively. Meanwhile, the successful separation of these electron–hole pairs largely determines the likelihood of their participation in useful redox reactions at the photocatalyst surface.⁷ Limitations of single-component photocatalysts are depicted in Fig. 1b.

2. Development of S-scheme photocatalytic mechanisms

Despite the great improvements achieved so far, single-component photocatalysts demonstrate limited photocatalytic activity.^{8–11} Joining two different semiconductors forming a heterojunction has attracted wide attention from the scientific community due to its potential to diminish charge recombination and steer charge carrier transfer and accumulation at disparate positions for effective consumption for surface redox reactions.¹² Various heterojunction configurations, including type-II heterojunctions, and Z- and S-scheme mechanisms, have been employed and developed to mitigate the recombination issue of photogenerated charge carriers in a single photocatalyst and enhance charge separation.^{11,13,14}

The charge transfer route of a typical type-II heterojunction is depicted in Fig. 2. After semiconductor 1 (S1) and semiconductor 2 (S2) are excited by light, they generate electrons and holes in their respective CB and VB. Due to the difference in the positions of the CB and VB of S1 and S2, electrons will spontaneously flow from the S2 CB with a higher energy to the S1 CB with a lower energy. Meanwhile, holes will transfer conversely from the S1 VB to the S2 VB (Fig. 2a). Theoretically, these charge transfers can achieve charge separation; however, type-II heterojunctions face thermodynamic, kinetic, and energetic challenges. From a thermodynamic viewpoint, charge migration in type-II heterojunctions results in an unfavorable energy waste because electrons and holes with higher reduction and oxidation potentials are transferred to new positions with

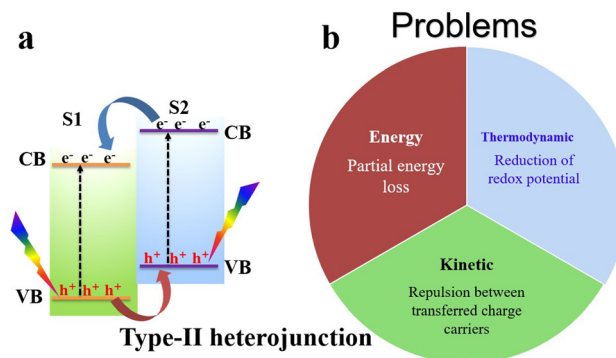


Fig. 2 (a) Schematic illustration of the charge transfer route in type-II heterojunctions. CB, VB, S1, and S2 correspond to the conduction band, valence band, semiconductor 1, and semiconductor 2, respectively. (b) Illustration of the limitations of type-II heterojunctions.

lower potentials, respectively, reducing their redox abilities. Moreover, from a kinetic point of view, the strong Coulombic repulsion arising between electrons (in S1 and those transferred from S2) and holes (in S2 and those transferred from S1) should disfavor the transfer and accumulation of a charge carrier onto a disparate semiconductor, which hampers the efficiency of photocatalytic reactions.⁸ Even more, this transfer is associated with partial energy loss after photogenerated electrons and holes transition from higher to lower energy positions.^{8–10}

Inspired by the natural photosynthesis process, Z-scheme charge transfer modes were also proposed. The traditional Z-scheme, proposed by Bard in 1979,¹⁵ involves a liquid-phase redox mediator (*e.g.*, $\text{Fe}^{3+}/\text{Fe}^{2+}$), mediating charge transfer and maintaining photogenerated electrons and holes with high redox potential (Fig. 3a, left). Consequently, charge carriers with strong redox abilities are preserved. However, conceptually, this mechanism has several inconsistencies that make its validity doubtful.¹⁶ First, the actual charge separation pathway is opposite to the proposed one. Photogenerated electrons at the CB of S2 tend to be transferred to recombine with holes at the VB of S1. Thus, the resulting electrons and holes after charge migration in the heterojunction have the lowest redox potential (Fig. 3a, right). Secondly, the Brownian motion of photocatalyst particles causes continuous movement (Fig. 3b, left), so the distance between S1 and S2 successively changed making charge migration aleatory. Furthermore, the thermal motion of the ionic mediator leads to its random diffusion to other areas, which cannot ensure the position of ions between S1 and S2 (Fig. 3b, middle). Furthermore, most photocatalytic reactions are performed under continuous stirring to ensure disorder in the system. Of note, the Z-scheme system is not in stillness, but in a moving state. These factors make the traditional Z-scheme mechanism problematic and correspond to an inaccurate description of the photocatalytic mechanism (Fig. 3b, right).¹⁷

To expand the scope of traditional Z-scheme configurations, the second generation of Z-scheme systems *i.e.* an all-solid-state Z-scheme, was developed in 2006 by Tada and coworkers.¹⁸ In this mechanism, a solid conductor (such as noble metal nanoparticles



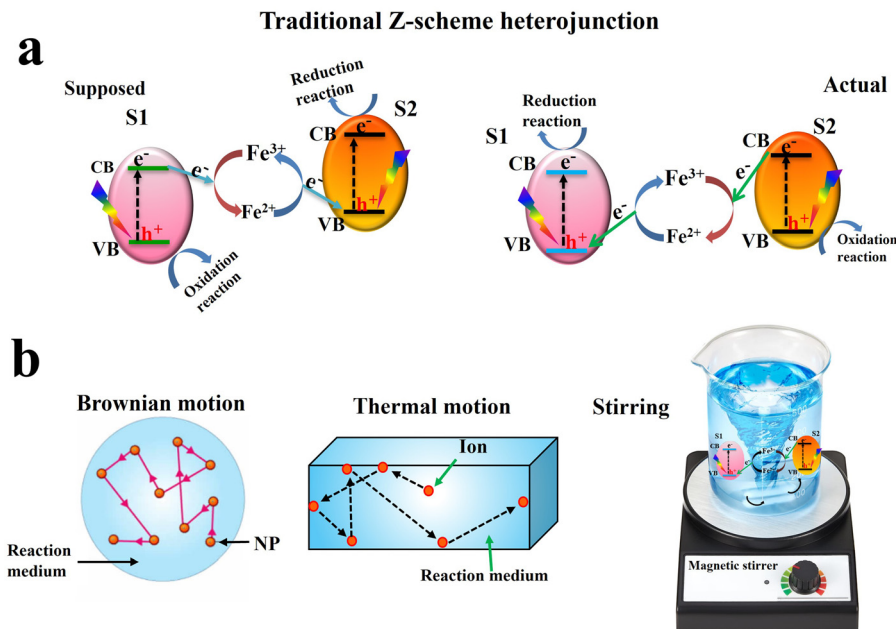


Fig. 3 Schematic illustration of the charge transfer route (a) and corresponding problems (b) in traditional Z-scheme heterojunction.

(Au, Ag), graphene (G), and graphene oxide (GO), *etc.*) is used as an electron mediator (Fig. 4a, left). Although it has broadened applicability, the all-solid-state Z-scheme mechanism is also wrong from different viewpoints.^{8,10,16,17} (1) The actual charge transfer direction is still the same as that in traditional Z-schemes. In other words, photogenerated electrons at the CB of S2 should migrate to recombine with holes at the VB of S1. Thus, charge carriers with lower redox potentials are retained (Fig. 4b, right). (2) Since the Fermi level (E_F) of most solid conductors is usually lower than that of S1 and S2 (Fig. 4b left), electrons from S1 and S2 will transfer to the conductor after they come into close contact until Fermi levels are aligned. Consequently, a Schottky junction (Φ_S) between the solid mediator and S1 or S2 will be formed. Unfortunately, this Schottky junction prevents the continuous transfer of photogenerated electrons from S1 to the mediator and finally to S2 (Fig. 4b right). (3) From a preparation viewpoint, it is challenging to precisely allocate the solid mediator just between the two photocatalysts *ca.* S1 and S2. Instead, the solid conductor should be randomly deposited over the external surface (Fig. 4c). For these reasons, it is concluded that the assumption of the all-solid-state Z-scheme mechanism raises serious conceptual concerns.^{16,19}

To tackle the problems of type-II heterojunctions, the third generation of Z-scheme systems, namely the direct Z-scheme mechanism, was first proposed in 2013 by Yu and colleagues.²⁰ For the direct Z-scheme mechanism, no electron mediator is required and S1 and S2 come into close contact. However, since 2019, it has been found that its first and second generations are regarded as problematic and incomplete.^{16,17,19} Therefore, in 2019, Yu's group again proposed the concept of the Step-scheme (S-scheme) mechanism to describe the charge transfer process over the $\text{WO}_3/\text{g-C}_3\text{N}_4$ photocatalyst.²¹

In a typical S-scheme heterojunction system, two semiconductors (namely the reduction photocatalyst (RP) and oxidation

photocatalyst (OP)) with staggered band positions come into contact with each other (Fig. 5, left).^{7,22–24} The RP should possess a higher CB position and Fermi level, while the OP has a relatively lower CB and Fermi level. When both components come into contact, the difference in their work functions culminates in an interfacial electron transfer from the RP to OP. This electron redistribution leads to band bending. Concurrently, the interface region from the RP sides becomes positively charged. Contrarily, the interface region from the OP side becomes negatively charged (Fig. 5, center). Under these circumstances, an internal built-in electric field (IEF) is established at the interface, whose direction points from the RP to OP. Upon light irradiation, electrons are excited from the VB to the CB of each respective photocatalyst. The IEF drives photogenerated electrons from the OP to recombine with holes in the VB of the RP. Meanwhile, useful photogenerated electrons and holes at the RP CB and OP VB with the highest reduction and oxidation potentials are maintained to trigger redox reactions, respectively (Fig. 5, right). The IEF provides a driving force for carrier transfer and separation, thus, regulating their behavior and kinetics. The S-scheme charge transfer mechanism not only realizes charge separation and transfer over the entire system but also suppresses charge recombination within the OP or RP itself thus maintaining their potential for effective redox reactions.^{7,8,25–28}

From the viewpoints of explaining the enhanced photocatalytic activity, maintaining high redox ability of photogenerated charges, and fostering spatial separation of charge carriers and alleviating their detrimental recombination, the S-scheme mechanism presents an adequate conceptual framework for achieving these pursuits. Additionally, S-scheme heterojunction photocatalytic systems have been proven to have promising potential for offsetting the limitation of single component photocatalysts regarding: (i) the severe recombination of photogenerated electron-hole pairs due



All-solid-state Z-scheme heterojunction

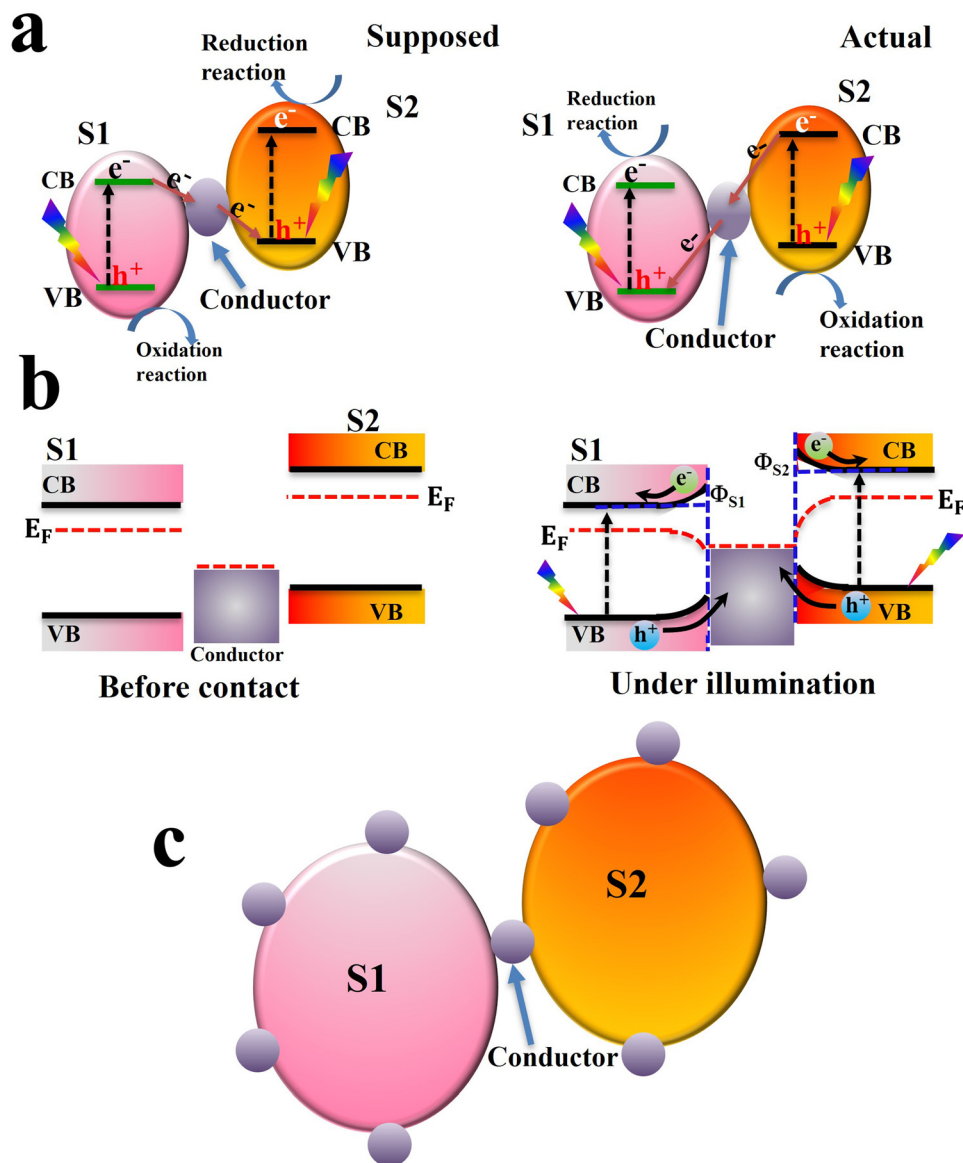


Fig. 4 Schematic illustration of the charge transfer route and corresponding problems in all-solid-state Z-scheme heterojunction systems. (a) Proposed (left) and most probable (right) charge transfer pathway; (b) schematic diagram showing the Schottky junction formation between semiconductors and the solid conductor, before contact (left, E_F referring to the Fermi level) and under light (right, Φ refers to the Schottky junction); and (c) an illustration displaying the random distribution of the solid conductor over the external surface of heterojunction components highlighting that only a few of these nanoparticles (NPs) are located properly between S1 and S2 semiconductors.

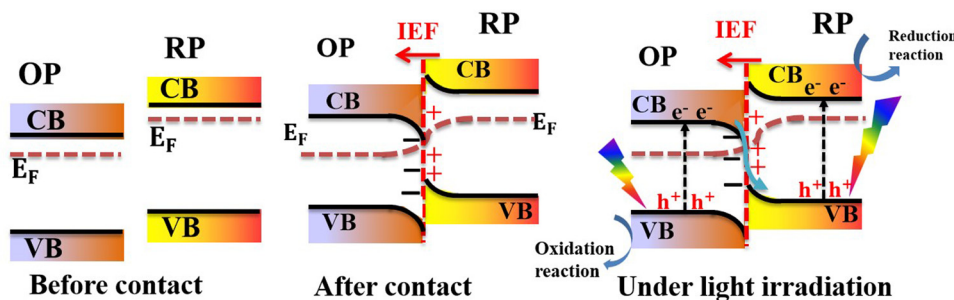


Fig. 5 Schematic illustration of the charge transfer mechanism in S-scheme heterojunctions.



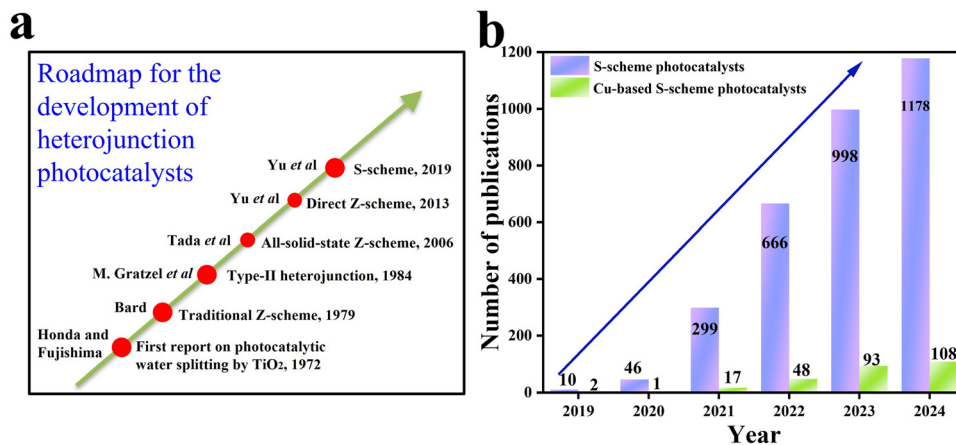


Fig. 6 (a) Historical development of concepts to explain heterojunction photocatalysts since the first report on photoelectrocatalytic water splitting by Honda and Fujishima. (b) Number of publications retrieved using the keywords “photocata* and S-scheme” or “photocata* and step-scheme” or “photocata* and s-type” in blue bars and “CuO* and S-scheme” or “Cu₂O* and S-scheme” or “CuWO₄* and S-scheme” or “CuBi₂O₄* and S-scheme” or “CuFe₂O₄* and S-scheme” and so on presented in green bars. The results were obtained from a Web of Science Core Collection search on December 11, 2024.

to the strong Coulombic attraction acting between them. (ii) The limited light absorption and failure to fully utilize the wide spectrum of the solar irradiation. And (iii) the weak redox potential due to limited bandgap size.

In view of the previous considerations, it appears clear that the emergence of S-scheme heterojunctions represents a step forward to a better understanding of charge carrier migration in heterojunctions. The historical development of different concepts of heterojunction photocatalysts is presented in Fig. 6a. Since the foundation of the S-scheme charge transfer concept in 2019, several thousands of research studies have been devoted to the construction and application of S-scheme heterojunctions in the field of photocatalysis.^{28–30} Fig. 6b shows the number of publications on the topic of S-scheme heterojunctions according to the Web of Science database.

3. Copper-based photocatalysts in S-scheme heterojunctions

TiO₂, ZnO, and g-C₃N₄ photocatalysts are extensively researched as useful components for S-scheme construction.^{31,32} In this vein, copper (Cu) is a versatile transition metal with excellent electrical and thermal properties.^{33,34} With multiple oxidation states and suitable abundance in the Earth’s crust, Cu is found in many formulations including pure metallic Cu, oxides (CuO and Cu₂O), sulfides (Cu_xS, (1 ≤ x ≤ 2)), selenides (CuSe), and basic carbonate (Cu₂CO₃(OH)₂), among others. Of the different oxidation states, Cu(I) and Cu(II) are the most commonly found, showing diverse activity in many catalytic applications.^{35,36} Regarding photocatalytic applications, Cu-based semiconducting materials are characterized by narrow bandgaps, allowing them to absorb in the visible light region of the solar spectrum with a large absorption coefficient (~10⁵ cm⁻¹) and suitable band positions.^{37,38} Fig. 7 depicts the bandgap and band positions of the most studied Cu-based photocatalytic materials, along with the benchmark TiO₂ and ZnO for comparison. The

redox potentials of the most common photocatalytic reactions have also been indicated. Additionally, Table 1 summarizes some of the optical and electronic properties of Cu-based photocatalytic materials discussed in this review.

Due to the aforementioned merits and considering the affordable cost of Cu, Cu-based materials are widely exploited as photocatalytic scaffolds in different applications such as HERs,^{33,46,47} CO₂ reduction,^{48–50} H₂O₂ generation,^{51,52} and pollutant degradation.^{53–55} In particular, due to their upgraded activity, improved stability, and selectivity, Cu-based S-scheme heterojunction photocatalytic systems are among the preferred materials within the realm of photocatalytic applications. Therefore, their integration into S-scheme heterojunctions has been continuously growing in recent years (Fig. 6b).

Cu-based photocatalytic materials can be categorized as either RPs or OPs according to their electronic structure. However, many members of the family possess suitable band structures to accomplish dual functionality *i.e.* RP or OP, depending on the accompanying counterpart. Fig. 7 categorizes Cu-based photocatalytic materials on this basis. As can be seen, Cu-based photocatalytic scaffolds present diverse entities whether as RPs or OPs. Yet, all of them exhibit narrow bandgap characteristics. Consequently, these materials represent a variety of choices for constructing efficient S-scheme photocatalytic systems for specific purposes.

Excellent reviews have been devoted to highlighting the synthesis, modification, and integration of Cu-based scaffolds in photocatalytic applications. For instance, Gawande and Goswami comprehensively reviewed the synthesis and modifications of Cu NPs and related nanomaterials and their manipulation in catalysis.³⁵ The recent advances in Cu-based nanocomposite photocatalytic materials for CO₂ conversion into solar fuels have also been reviewed.³⁸ Recently, general aspects regarding the synthesis, modifications, and applications of Cu-based photocatalysts have been summarized.^{33,37} However, a thorough review of recent advances regarding Cu-based S-scheme photocatalytic systems is still missing. Here, we comprehensively discuss up-to-date progress in Cu-based materials including oxides (Cu₂O and CuO), binary oxides



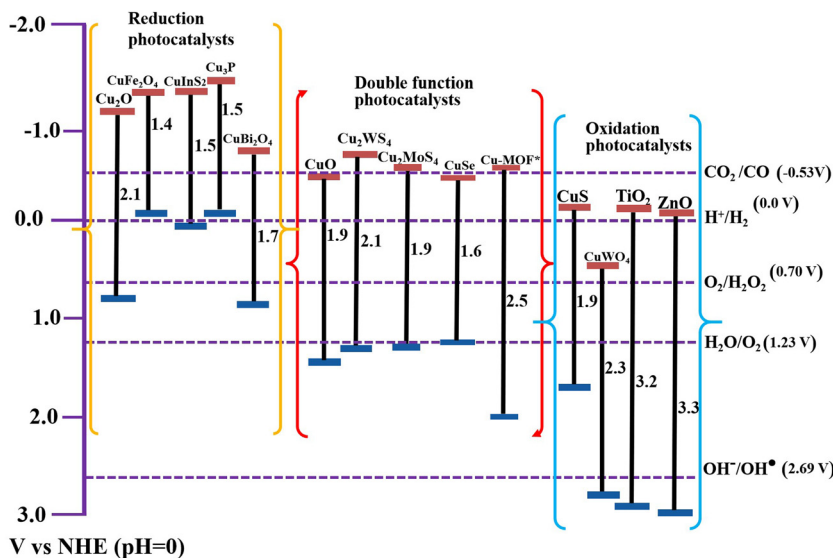


Fig. 7 Bandgaps and band positions of the Cu-based photocatalytic materials discussed in this review (as reported in the corresponding references). Benchmark TiO₂ and ZnO photocatalysts are provided for comparison. * Cu-MOF refers to the Cu-BTC MOF.³⁹

(CuBi₂O₄, CuFe₂O₄ and CuWO₄), chalcogenides (CuS, CuSe and Cu-based binary sulfides), Cu-phosphides (Cu₃P) and Cu-MOFs, among others, forming part of S-scheme heterojunction photocatalytic systems. As a hot topic in the realm of photocatalysis, design principles and verification approaches for S-scheme heterojunctions will be presented. The synthetic strategies and brief descriptions of characterization data for relevant examples of the aforementioned Cu-based photocatalytic materials will be introduced. Current gaps and future research opportunities will also be provided. We aim to provide a detailed overview of the Cu-based materials that have so far been integrated in S-scheme photocatalytic systems to show the progress in the field to a broad community belonging to different disciplines such as chemical engineering, organic and inorganic chemistry, materials science and solar energy utilization, among others.

4. Design of copper-based S-scheme photocatalysts

In general, a typical S-scheme heterojunction system contains two photocatalytic scaffolds with suitable band structures and close interfacial contact, allowing charge migration following the S-scheme configuration driven by the built-in IEF. Different combinations of OPs and RPs with distinct p- and n-type semiconducting characteristics can fulfill the requisites of S-scheme heterojunction configurations. Generally, four combinations of n- and p-type semiconductors can be integrated to establish S-scheme configurations. These include n-n, p-p, n-p, and p-n heterojunctions. This fact offers multiple choices for constructing S-scheme systems yet all these combinations follow the same charge transfer mechanism. Fig. 8 shows various combinations of n- and p-type semiconductor photocatalysts to construct S-scheme heterojunctions.

Consistently in this review, the OP is written first, followed by the RP. For example, in the CuO/In₂O₃ S-scheme heterojunction, CuO acts as the OP, while In₂O₃ serves as the RP. Generally, the classification of photocatalytic components in S-scheme heterojunctions into OP and RP relies mainly on their Fermi levels and VB and CB positions. A photocatalyst with a higher Fermi level and CB in the junction will act as the RP where reduction reactions occur. Meanwhile, the other photocatalyst with lower Fermi levels, CB, and VB energy values will be the OP, where oxidation reactions take place. From thermodynamic and kinetic viewpoints, it is desirable to effectively accomplish photocatalytic reactions through S-scheme heterojunctions in which RP and OP possess suitable CB and VB positions *i.e.* more negative and more positive, respectively. Therefore, photogenerated electrons and holes located at the RP CB and OP VB, respectively, have adequate potential to trigger redox reactions with suitable yields and fast rates.

Table 1 summarizes the semiconducting type, bandgap, CB position, and work function of most Cu-based photocatalysts discussed in this review. Cu-based photocatalytic materials

Table 1 Selected characteristics of the studied Cu-based photocatalytic materials. Data are extracted from relevant ref. 37 and 40–45

Cu-based photocatalyst	Semiconductor type	Bandgap (eV)	CB position (V vs. NHE, pH = 0)	Work function (eV)
Cu ₂ O	p	2.0–2.2	–1.2	4.9
CuO	p	1.5–1.9	–0.4	5.5
CuBi ₂ O ₄	p	1.8	–0.8	4.8
CuFe ₂ O ₄	p	1.4	–1.3	5.4
CuWO ₄	n	2.3	+0.4	5.2
CuS	p	1.9–2.1	–0.3	6.5
CuInS ₂	p	1.5–1.8	–1.4	4.2
Cu ₂ WS ₄	n	2.1	–0.8	5.1
CuSe	p	1.3–1.6	–0.4	5.1
Cu ₃ P	p	1.5	–1.6	4.7
Cu-MOF	n	2.5	–0.6	5.2



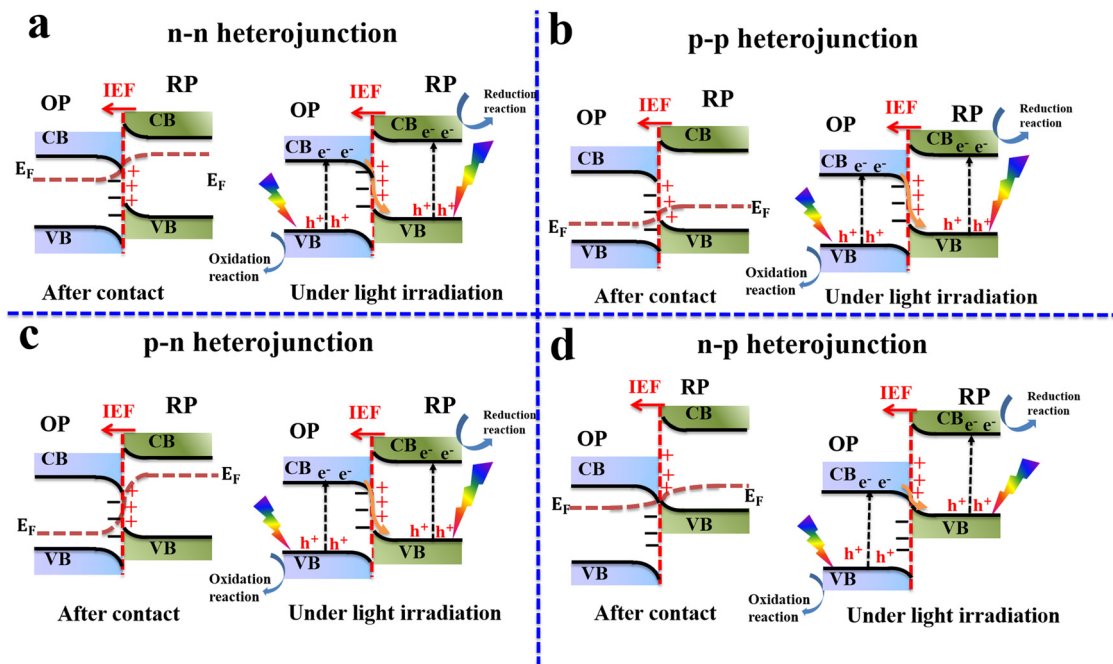


Fig. 8 Four types of S-scheme heterojunctions formed between: (a) n–n OP and RP, (b) p–p OP and RP, (c) p–n OP and RP, and (d) n–p OP and RP. In these combinations, electrons are transferred from the RP to the OP after contact. However, after irradiating the system with light, photogenerated electrons are transferred in the opposite direction under the IEF's driving force.

provide versatile choices for designing S-scheme heterojunctions for different target applications. In this context, some Cu photocatalysts can be exclusively RP or OP. Meanwhile, there are still photocatalysts with suitable band positions that exhibit dual functionality depending on the other component in contact.

Beyond the typical requirements to construct S-scheme heterojunctions, the stability of individual components should be considered for effective and practical applications. For instance, Cu_2O and CdS are sensitive to surface corrosion by photogenerated holes. Therefore, their integration as a OP in S-scheme heterojunctions is unfavorable from a stability standpoint.

5. Characterization of S-scheme photocatalysts

Since the S-scheme charge transfer mechanism describes the process of electron transfer and separation among two combined semiconductors with staggered band positions *i.e.* OP and RP,^{10,25,56} diverse tools can be deployed to interpret the existence of such charge movement and space separation. The most adopted approaches so far are *ex situ/in situ* irradiated X-ray photoelectron spectroscopy (ISIXPS), surface potential measurement, and DFT calculations.^{7,28} Recently, femtosecond transient absorption spectroscopy (fs-TAS) has emerged as a powerful tool to study the charge transfer dynamics in heterojunction photocatalysts.⁵⁷ The next sections aim to shed light on these tools, explaining how to confirm the occurrence of S-scheme charge transfer action.

5.1. *Ex situ/in situ* irradiated X-ray photoelectron spectroscopy (ISIXPS)

XPS has been widely utilized to analyze the composition of a material as well as the chemical state of elements. In principle, it is a surface-specific spectroscopic technique based mainly on light–matter interactions. When an X-ray photon with energy higher than the sample ionization impinges into the sample surface (Fig. 9a), it induces the ejection of a core electron with a kinetic energy that is determined by the electron binding energy (BE) of the ejected electron and photon energy (eqn (1)):

$$E_{\text{kinetic}} = h\nu - E_{\text{binding}} \quad (1)$$

The identity of each element in the sample is correlated to its BE, as this is a characteristic physical property of that element. The XPS spectrum depicts the intensity of emitted electrons as a function of BE.

The electron BE value is determined by the interplay between two forces *i.e.* the Coulombic attraction between the nucleus and electrons and Coulombic repulsion among the electrons themselves. Therefore, any change in the element's electronic density and/or valence state will imply a corresponding change in its BE, known as a chemical shift. For a specific element, if the electron density over it increases, its electronic BE decreases. Contrarily, if the electron density decreases, its BE increases.

Within a heterojunction, charge transfer from one semiconductor to another induces an electron density difference with respect to both components individually, which can be probed directly from the change in BE values (*ex situ* XPS). A positive change in the BE of an element within a given semiconductor



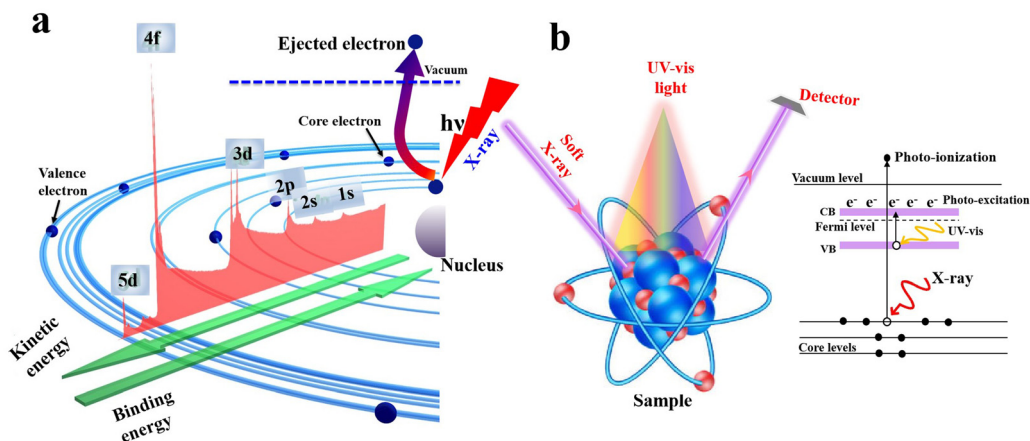


Fig. 9 (a) Schematic illustration of the XPS working principle. (b) Illustration of ISIXPS measurements.

implies that electrons move from this semiconductor to the other, and *vice versa*. In addition, ISIXPS is used to probe the change in BE of constituent elements under the influence of irradiation light compared to in the dark (Fig. 9b). When the heterojunction is irradiated by UV-vis light during XPS measurement, valence electrons are excited from the VB to CB (photo-excitation, Fig. 9b). Photoexcited electrons are distributed across the interface of the heterojunction. Electron migration from one component to the other culminates in electron density depletion and accumulation regions, respectively. This charge gradient will induce BE shifts upon illumination compared to under

dark conditions. This measurement can provide direct experimental evidence for the charge transfer within the heterojunction during the photocatalytic reaction. Under these circumstances, BEs of constituent elements that belong to regions of electron deficiency will be shifted to higher values and *vice versa*. For example, ZnO and CuInS₂ can form an S-scheme heterojunction, with the band diagram presented in Fig. 10a.⁵² Taking into account the higher position of the Fermi level (E_F) of CuInS₂ compared with that of ZnO, electrons are expected to move from the higher E_F to lower E_F *i.e.* from the CuInS₂ side to the ZnO side until equilibrium is reached.

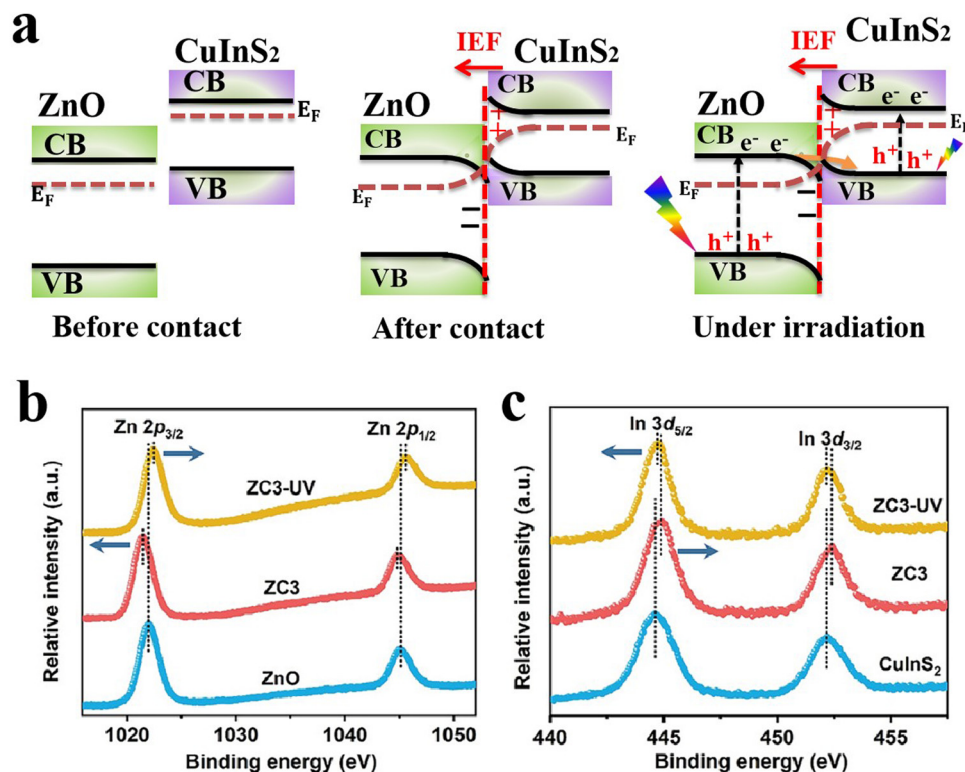


Fig. 10 (a) Schematic representation of the band structure of ZnO and CuInS₂ and the interfacial electron transfer between them both after contact and under light exposure. *Ex situ* and ISIXPS spectra of (b) Zn 2p and (c) In 3d recorded for ZnO, CuInS₂, and the ZnO/CuInS₂ composite in the dark and under UV irradiation. (b) and (c) were reproduced with permission.⁵² Copyright 2024, Wiley-VCH.



Such electron redistribution will indeed induce a change in the electron density of the elements involved in the process, resulting in a decrease and increase in the electron density over CuInS₂ and ZnO, respectively. Thus, the BE of constituent elements will change accordingly. As shown in Fig. 10b and c, the BEs of Zn 2p are shifted toward lower values after contacting CuInS₂ compared to pristine ZnO (bottom and middle charts of Fig. 10b). In contrast, the BEs of In 3d are relocated to higher values (bottom and middle plots in Fig. 10c).⁵² These shifts in BE values confirm that electrons migrate from CuInS₂ toward ZnO during hybridization. Under light irradiation, ZnO and CuInS₂ will be respectively excited. The photogenerated electrons will transfer in the opposite direction, *i.e.* from ZnO to CuInS₂ under the influence of the IEF (Fig. 10a), resulting in a different electron density change and hence a chemical shift over each component (Fig. 10c). The combined results confirmed that charge is transferred within the ZnO/CuInS₂ heterostructure according to the S-scheme mechanism, with electrons moving from the RP (CuInS₂) to OP (ZnO) after contact. Meanwhile, photogenerated electrons migrate in the opposite direction under light excitation. The ISIXPS technique has been extensively employed to verify the occurrence of a charge transfer according to the S-scheme configuration in heterojunction photocatalysts.

5.2. Surface potential

Kelvin probe force microscopy (KPFM) is a tool that enables imaging of the surface potential on a broad range of materials at the nanometer scale. It can measure the contact surface potential of the sample (work function) by monitoring the contact potential difference (CPD) between the atomic force microscopy (AFM) tip and the sample (Fig. 11). The CPD between the tip and sample is defined as:⁵⁸

$$\text{CPD} = \frac{\Phi_{\text{tip}} - \Phi_{\text{sample}}}{-e} \quad (2)$$

where Φ_{tip} and Φ_{sample} are the work functions of the tip and sample, and e is the electronic charge. During operation, the AFM tip is brought in contact or close to the sample surface (Fig. 11a), connecting both electrically. Due to the difference in Fermi levels, charges are redistributed between the tip material and the sample until their Fermi energy levels are aligned.

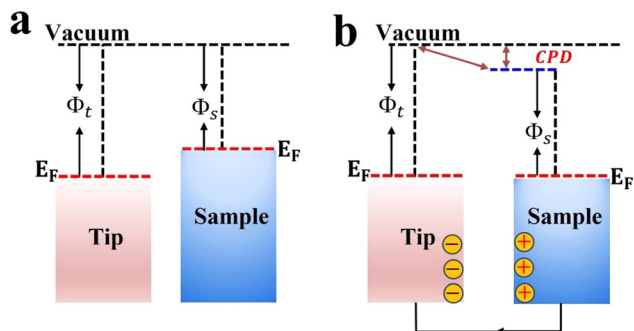


Fig. 11 Schematic illustration of the KPFM working principle before (a) and after (b) electrical contact.

Therefore, the tip and sample surface become charged, and an apparent electrical potential is generated over the contact area *i.e.* CPD (Fig. 11b).⁵⁸ To accurately measure the CPD, an applied external bias is applied in the opposite direction to the established electrical force. The amount of applied bias that nullifies the electrical force is thus equal to the work function difference between the tip and sample, and hence the CPD. Given that the work function of the tip is known; the work function of the sample can be calculated.

For heterojunction systems where charges are distributed between individual components after coming into contact, KPFM can be used to map the potential difference over the composite sample under dark and light conditions. By comparing the CPD of pure components with that of the composite sample in the dark and upon illumination, the redistribution of electron density can be probed. For example, the charge transfer dynamic was investigated over pyrene-*alt*-dibenzothiophene *S,S*-dioxide (P16PySO)/WO₃ S-scheme heterojunctions using KPFM imaging (Fig. 12).⁵⁹ The three-dimensional surface potential imaging shows the composite heterojunction (PW10) under dark and light conditions (Fig. 12a). Components A and B in Fig. 12a represent P16PySO and WO₃, respectively. Under light, the CPD of WO₃ (point B) was significantly increased by 17 mV compared to that in the dark (Fig. 12b). This finding implies that photogenerated electrons migrate from WO₃ to P16PySO driven by the built-in IEF in accordance with the S-scheme charge transfer configuration. Given that the work functions of P16PySO and WO₃ were calculated to be 4.46 and 4.75 eV, respectively, the charge transfer pathway over the P16PySO/WO₃ S-scheme heterojunction can be drawn as in Fig. 12c. In this regard, WO₃ and P16PySO serve as the OP and RP in the PW composite.

Generally, CPD is a suitable technique to predict charge movement between semiconducting components in S-scheme heterojunction photocatalysts.

5.3. Density functional theory (DFT) simulations

The charge density is a core quantity in DFT calculations and it can be utilized for different aspects of materials science from bonding to determining charge transfer between specific atoms.⁶⁰ In photocatalytic heterojunctions, DFT simulations have been extensively utilized to elucidate the charge density difference across the heterojunction interface. The results predict the differential electrostatic potential along a perpendicular plane to the heterojunction surface based on charge distribution between the components across the interface. In this vein, charge will flow from a material with a lower work function to another with a higher work function. As an example, the charge density difference across the CuFe₂O₄/ZnIn₂S₄ interface heterojunction has been simulated (Fig. 13). The work functions of CuFe₂O₄ ($\Phi = 5.36$) and ZnIn₂S₄ ($\Phi = 6.74$) were calculated based on DFT principles. Fig. 13a depicts band structures for both components. After contact, due to the difference in the Fermi levels, electrons are transferred from CuFe₂O₄ to ZnIn₂S₄. As a result, electron depletion (cyan area) and accumulation (yellow area) regions are found on CuFe₂O₄ and ZnIn₂S₄ sides, respectively (Fig. 13b). The Bader charge analysis results (Fig. 13c) indicated the transfer of $0.75e^-$ per molecule from CuFe₂O₄ to



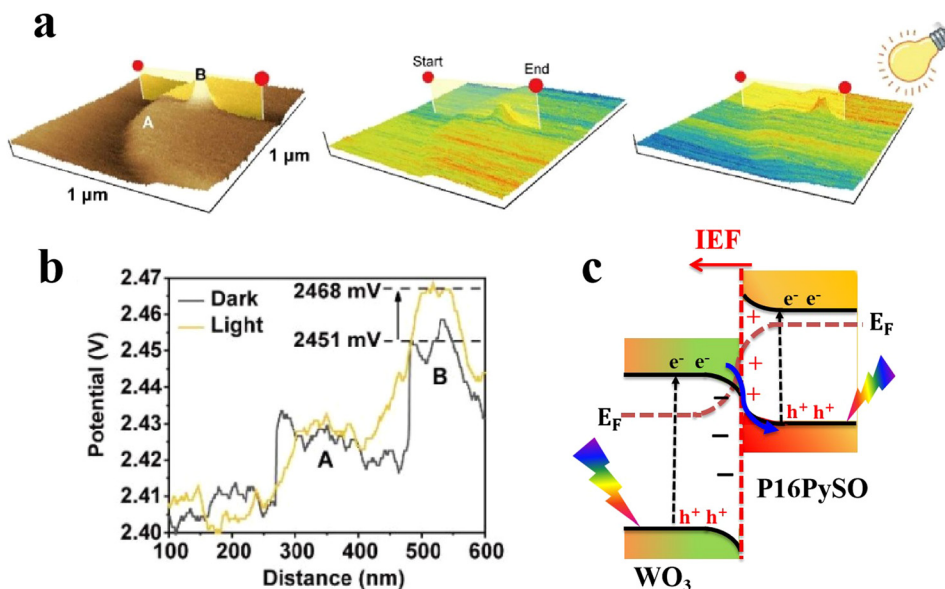


Fig. 12 (a) Atomic force microscopic image of PW10 (left), and the 3D KPFM surface potential distribution for PW10 under dark (middle) and light (right) conditions. (b) Corresponding line-scanning of CPD for PW10 in the dark and under light.⁵⁹ Reproduced with permission. Copyright 2023, American Chemical Society. (c) Band structure and proposed charge transfer pathway over the P16PySO/WO₃ S-scheme heterojunction.

ZnIn₂S₄ through the interface, further demonstrating the unique charge transfer mechanism.⁶¹ Validation of DFT theoretical calculations with experimental data has confirmed DFT as a powerful tool for predicting the charge distribution across the heterojunction interface. Besides, the assignment of active sites and determination of reaction mechanisms and kinetics have become feasible theoretical tasks.

5.4. Femtosecond transient absorption spectroscopy (fs-TAS)

Fs-TAS is a powerful technique for monitoring the dynamics of photogenerated electrons and holes in heterojunction photocatalysts.⁵⁷ The time-resolved spectroscopic technique is adopted to explore the relaxation pathways of excitons on a picosecond-to-femtosecond time scale and measure the lifetime of photogenerated electrons and/or holes after their generation. A typical fs-TAS spectrophotometer consists of four main parts *ca.* a laser source, optical parametric amplifier (OPA), delay system, and detector (Fig. 14). In detail, a conventional femtosecond Ti-sapphire laser source produces laser pulses of 800 nm. This main beam is split into two beams *viz.* a pump beam and a probe beam. The pump beam is converted into shorter wavelengths (320–700 nm) by the OPA and passes through a computerized optical chopper before exciting the target sample. The probe beam is delayed by a computer-controlled delay system and then focused on a sapphire crystal to generate a white light continuum that hits the sample cell. After passing through the sample, the transmitted white light beam is collected on the detector, while the pump beam is blocked. The pump beam reaches the sample first, causing the excitation of electrons from the ground state to the excited state. After being delayed, the probe white-light beam reaches the samples after a specific delay time with respect to the pump. Ground state and excitons (instantaneously generated by the pump pulse) can absorb some wavelengths of the probe

pulse. The differential transient absorption (ΔA) spectra of the sample are obtained by measuring the absorption caused by the probe pulse with and without pump pulse excitation, respectively. By changing the delay time, the number of excited states will also change, and so will ΔA . Therefore, the lifetime of charge carriers can be obtained by fitting the transient signal decay to first order or other kinetics equations.⁵⁷

For photocatalytic heterojunctions, the process of electron transfer across the interface can be supported by two features from fs-TAS analysis in comparison to the individual components. Firstly, a new relaxation pathway with an ultrafast lifetime exists within the spectrum of the heterojunction that is absent in the spectra of the pure components.⁶² Secondly, the lifetime of a specific charge carrier becomes longer after integrating within a heterojunction system. Observation of these two features implies that the target exciton is effectively separated across the interface, thereby providing spectroscopic evidence in support of the charge transfer step.⁶³

For example, the electron transfer process in the TiO₂/Bi₂O₃ heterojunction system was investigated by fs-TAS measurements performed on TiO₂ (TO) and TiO₂/Bi₂O₃ (TBO40, 40 represents the wt% of Bi₂O₃).⁶² Fig. 15a and b depict the ground state bleaching (GSB) peak at $\lambda \sim 395$ nm and the excited state absorption (ESA) peak at $\lambda \sim 425$ –550 nm in both TO and TBO40. The authors also recorded the fs-TAS spectra of TO with an electron scavenger (AgNO₃) to resolve the contributions from both excitons. According to the fitting results of GSB recovery kinetics (Fig. 15c), the τ_{ave} values of holes increase from 148.5 ps for TO-AgNO₃ to 232.5 ps for TBO40. The longer lifetime of photogenerated holes on the composite TBO40 than that in pure TO – even with an electron scavenger – implies the occurrence of an efficient electron transfer from TO (as OP) to BO (as RP) through an interfacial electron transfer from the CB of TiO₂ to the VB of Bi₂O₃ according to an



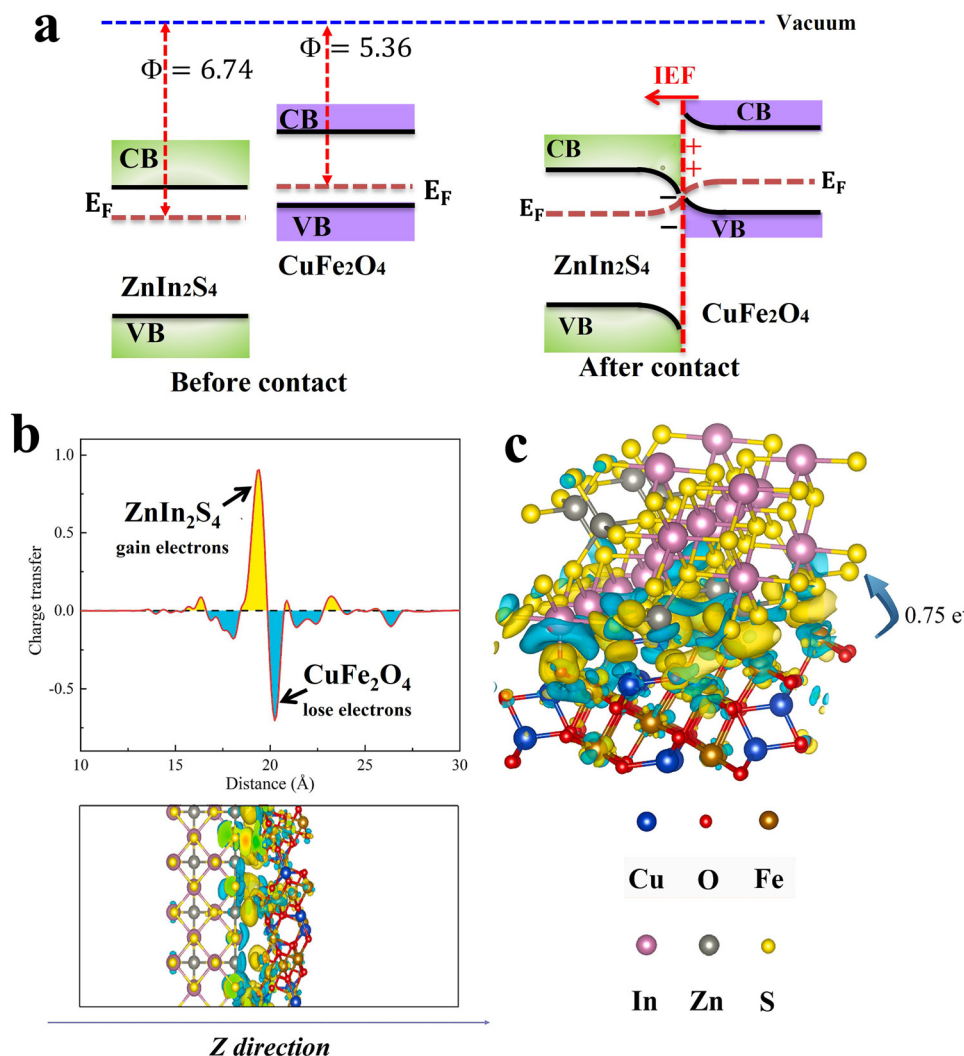


Fig. 13 (a) Schematic illustration of band structure and charge transfer between CuFe₂O₄ and ZnIn₂S₄. (b) The plane average charge density difference and Z-direction differential charge density map. (c) The differential charge density map, where the yellow and cyan electron clouds represent enhanced and depleted electron density with respect to the individual components. Reproduced with permission.⁶¹ Copyright 2024. Elsevier.

S-scheme mechanism (Fig. 15d). The emergence of new relaxation pathways was also reported for the In₂O₃/Nb₂O₅ heterojunction.⁶⁴ Generally, fs-TAS is a direct approach to probe the charge dynamics in S-scheme heterojunction photocatalysts. The emergence of a new relaxation pathway or the prolongation of the average lifetime of excitons is directly related to their possible separation and transfer across the interface.

6. Construction of Cu-based S-scheme photocatalysts

Various Cu-based photocatalytic materials described in the literature within the last four years as forming S-scheme heterojunctions will be thoroughly discussed, including Cu-oxides, Cu-binary oxides, Cu-chalcogenides, Cu-phosphides, and Cu-MOFs. These compounds possess fascinating structural, optical, and electronic properties. Additionally, they showed

promising photocatalytic activity. The crystal structures of these compounds are given in Table 2.

6.1. Cu-based oxides

This group includes Cu₂O, CuO, and Cu-based binary oxides. The next sections will discuss their integration into S-scheme heterojunctions with different photocatalytic scaffolds.

6.1.1. Cu₂O. Cuprous oxide (Cu₂O) is a p-type semiconductor with a narrow bandgap (2.0–2.2 eV) and significant absorption ability within the visible region. It exhibits effective photocatalytic activity in diverse applications. However, its poor oxidation resistance, strong photo-corrosion, and rapid charge recombination limit its practical integration in photocatalytic fields. Integrating Cu₂O in an S-scheme configuration with other semiconductors has culminated in an overall improved photocatalytic efficiency and minimized corrosion susceptibility. Theoretically, Cu₂O, as a p-type semiconductor, is expected to form an S-scheme heterojunction with other semiconductors based on three configurations (Fig. 8), in



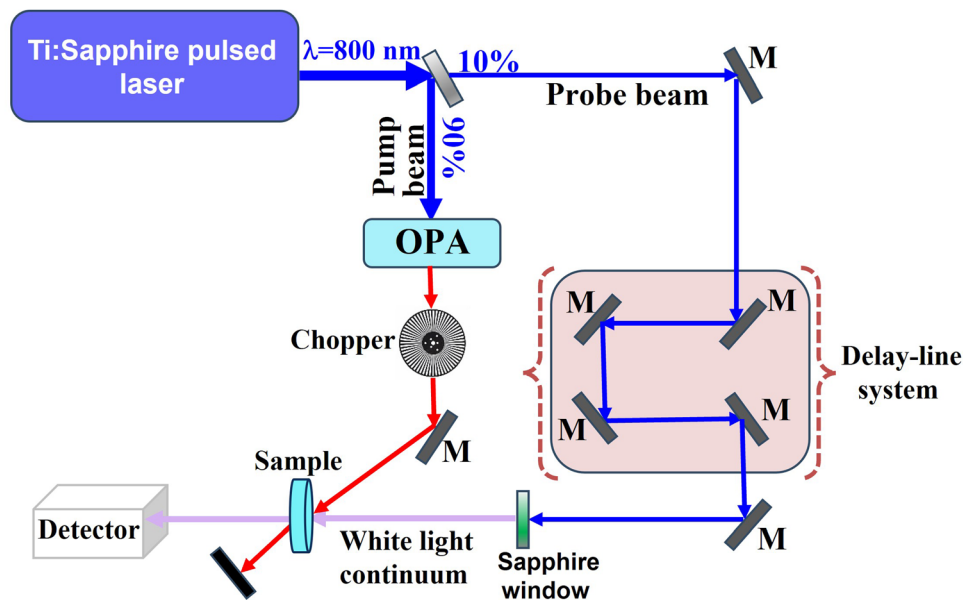


Fig. 14 Schematic layout of the fs-TAS apparatus setup. M: mirror; OPA: optical parametric amplifier.

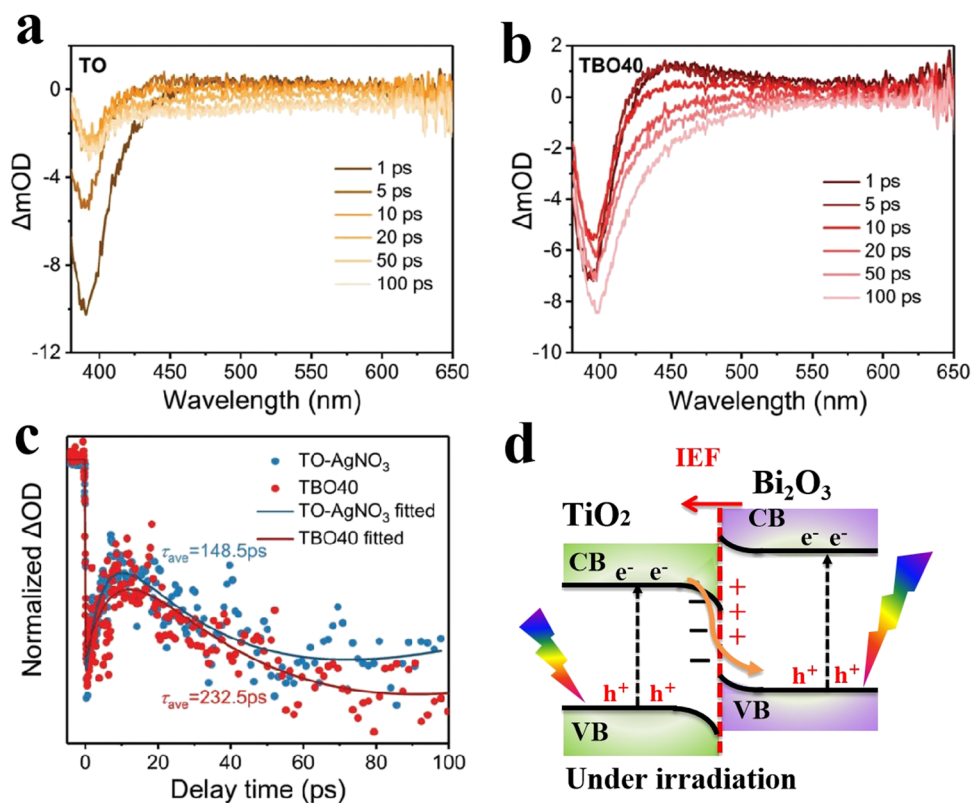


Fig. 15 fs-TAS of TiO_2 (TO, a) and $\text{TiO}_2/\text{Bi}_2\text{O}_3$ -40 (TBO40, b) recorded with 340 nm excitation. (c) Corresponding fit of the transient absorption kinetics for TO-AgNO₃ and TBO40 monitoring at 395 nm within a time window of 100 ps. Reproduced with permission.⁶² Copyright 2022, Wiley-VCH. (d) Schematic illustration of S-scheme charge transfer within the TBO40.

which Cu_2O can serve as the RP or OP. From a practical viewpoint, p-type Cu_2O may experience severe photo-corrosion due to the accumulated photogenerated holes if

employed as the OP. Therefore, it is reasonable to integrate Cu_2O as the RP with a suitable OP to achieve effective and stable S-scheme configurations. In such heterojunctions, the




photogenerated holes at the Cu_2O VB will be consumed by recombination with photogenerated electrons from the OP. Meanwhile, photogenerated electrons and holes at the Cu_2O CB and OP VB will be maintained to trigger reduction and oxidation reactions, respectively. The next sections will discuss different types of semiconducting materials with which Cu_2O can be combined to construct S-scheme heterojunctions. Table 3 summarizes the Cu_2O -based S-scheme photocatalysts applied for various catalytic applications.

6.1.1.1. Cu_2O /metal oxide S-scheme heterojunctions. Cu_2O can be combined with a wide range of metal oxides, such as CuO ,^{65,66} TiO_2 ,^{67,68} ZnO ,^{69,70} WO_3 ,^{71,72} $\text{W}_{18}\text{O}_{49}$,⁷⁴ Fe_2O_3 ,⁷⁷ and CeO_2 ,^{75,76} to form desirable S-scheme heterojunctions. For instance, when Cu_2O is combined with Ti^{3+} -doped TiO_2 , a robust structure with improved activity and stability is obtained.⁶⁷ The $\text{Cu}_2\text{O}/\text{TiO}_2$ S-scheme photocatalyst showed almost 100% degradation of 4-chlorophenol (4-CP) in 40 minutes, with a reaction rate *ca.* 510 times that of pristine Cu_2O and TiO_2 . The improved activity and stability were attributed to enhanced charge separation thanks to the S-scheme configuration that promotes interfacial charge transfer at the interface. Table 3 summarizes most reported S-scheme heterojunctions involving Cu_2O as a photocatalytic component for different applications.

The process of charge separation can be further strengthened after compositing the S-scheme system with cocatalysts or conductive additives such as carbonaceous materials (graphene,⁷⁸ carbon quantum dots (CQDs), N-doped carbon (NC)^{68,70}), metallic species^{66,73,93} and MXenes.⁸⁶ For example, Huang *et al.*,⁶⁸ found that the introduction of an NC-layer not only adjusted the Fermi level of TiO_2 , thus switching the interfacial charge transfer pathway from a p-n to S-scheme heterojunction, but also provided an accessible channel for effective charge separation and transfer. Additionally, metallic Ni was photodeposited over the TiO_2 -NC- Cu_2O composite to serve as an electron sink. The highest photocatalytic H_2 evolution rate of $13\,522\ \mu\text{mol g}^{-1}\ \text{h}^{-1}$ was attained for the composite sample containing the optimum percentage of NC and Ni, *ca.* 664 times higher than that of pure Cu_2O . The TiO_2 -NC- Cu_2O -Ni S-scheme system exhibited poor stability, with $\sim 15\%$ activity loss after 5 cycling tests. The authors employed ISIXPS to confirm the S-scheme charge transfer mechanism. Distinct peak shifts were observed for both Ti 2p and Cu 2p core levels in high-resolution XPS (Fig. 16a and b). Following a typical S-scheme charge transfer mechanism, charges are distributed at the interface after contact and hence an IEF is generated at the interface (Fig. 16c). Under light irradiation, photogenerated electrons at the TiO_2 CB are transferred driven by the built-in IEF, to recombine with photogenerated holes at the Cu_2O VB. Such charge transfer under illumination imparts corresponding shifts in Ti 2p and Cu 2p XPS peaks to higher and lower binding energies, respectively (Fig. 16a and b). Meanwhile, electrons at the Cu_2O CB and holes at the TiO_2 VB are maintained being responsible for reduction and oxidation reactions, respectively. Ni metallic species act as reservoirs to accumulate electrons from the

Table 2 Crystal structures of the Cu-based photocatalytic materials discussed in this review

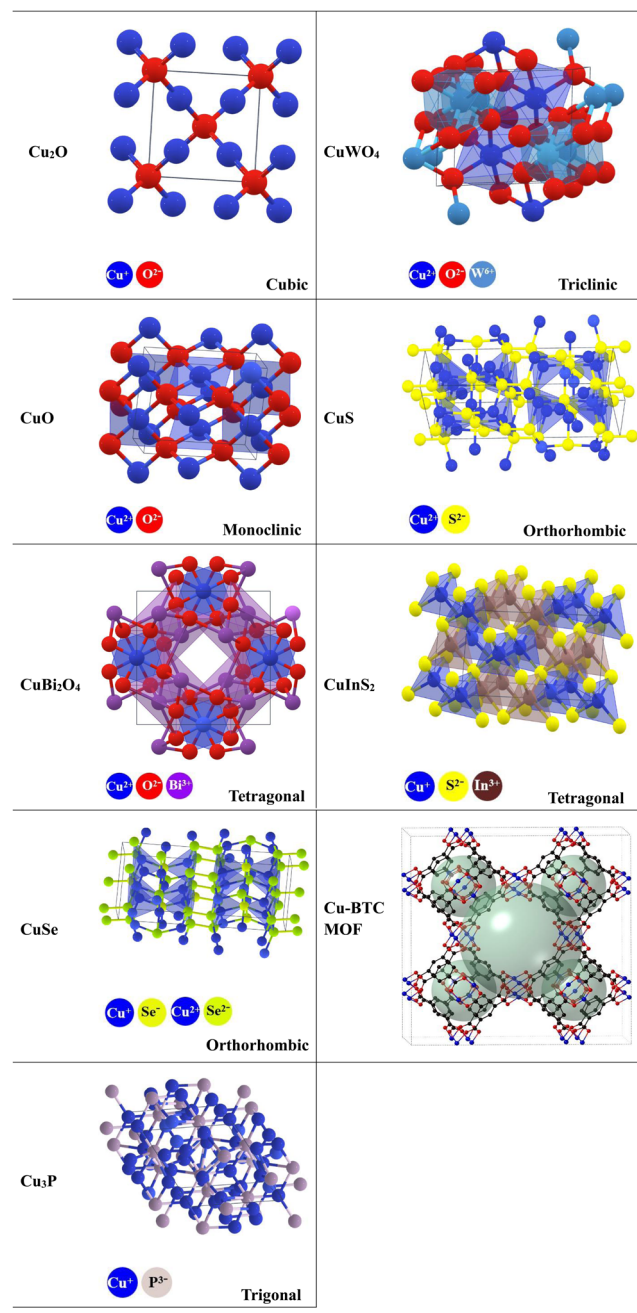

Cu_2O CB to boost the hydrogen evolution reaction.⁶⁸ A similar function as an electron accumulation center was reported for Ag NPs deposited over a $\text{Cu}_2\text{O}/\text{CuO}$ S-scheme heterojunction during methyl orange (MO) dye degradation and Cr(vi) reduction.⁶⁶

In light of these studies, conductive cocatalysts with excellent charge transfer ability and minimal photogenerated electron-hole pair recombination were found to dramatically enhance the charge separation over S-scheme heterojunctions, boosting further the photocatalytic activity. On the other hand,



Table 3 S-scheme heterojunction systems of Cu₂O combined with various photocatalytic scaffolds for different applications. The S-scheme heterojunctions are arranged as OP/RP

S-scheme heterojunction	Application	Efficiency	Ref.
CuO/Cu ₂ O	CO ₂ reduction	CO yield = 22.14 μmol g ⁻¹ h ⁻¹	65
CuO/Cu ₂ O	Methyl orange (MO) degradation and Cr(vi) reduction	Degradation = 96 and 81.8% for MO (20 min) and Cr(vi) (40 min), respectively	66
TiO ₂ /Cu ₂ O	4-CP degradation	100% degradation in 40 min	67
TiO ₂ /Cu ₂ O	H ₂ evolution	Evolution rate = 13 521.9 μmol g ⁻¹ h ⁻¹	68
ZnO/Cu ₂ O	H ₂ evolution	Evolution rate = 209 μmol g ⁻¹ h ⁻¹	69
ZnO/Cu ₂ O	Doxycycline hydrochloride (DCHCl) degradation and Cr(vi) reduction	Degradation = 92.9 and 88.9% for DCHCl and Cr(vi) in 90 min, respectively	70
WO ₃ /Cu ₂ O	Carbamazepine (CBZ) degradation and nitrobenzene (NB) reduction	94% CBZ degradation in 60 min and 88% photoreduction of NB into aniline was achieved in 150 min	71
WO ₃ /Cu ₂ O	Degradation of levofloxacin (LVX)	97.9% LVX degradation in 80 min	72
WO ₃ /Cu ₂ O	CO ₂ photoreduction	CH ₄ yield of 1.87 mmol g ⁻¹ within 18 h	73
W ₁₈ O ₄₉ /Cu ₂ O	N ₂ fixation	NH ₃ yield of 252.4 μmol g ⁻¹ h ⁻¹	74
Cu ₂ O/CeO ₂	H ₂ evolution	~100 μmol/5 h	75
CeO ₂ /Cu ₂ O	VOC degradation	Toluene, xylene and formaldehyde completely degraded in 70, 50 and 6 min, respectively	76
Fe ₂ O ₃ /Cu ₂ O	Benzyl amine (BA) oxidative coupling	Yield = 69.3%, after 6 h	77
Ag ₂ O/Cu ₂ O	<i>E. coli</i> disinfection	100% inactivation in 75 min	78
BiVO ₄ /Cu ₂ O	H ₂ O ₂ generation	H ₂ O ₂ yield of 112 μmol L ⁻¹ h ⁻¹	79
Bi ₂ WO ₆ /Cu ₂ O	Water oxidation	O ₂ yield of 50 μmol L ⁻¹ within 3 h	80
BiOBr/Cu ₂ O	CO ₂ reduction	CH ₄ yield = 22.78 μmol g ⁻¹ within 4 h	81
BiOBr/Cu ₂ O	Methylene blue (MB), rhodamine B (RhB), Congo red (CR), methyl viologen (MV) and tetracycline (TC) degradation	Degradation for RhB = 82.33%, CR = 94.57%, MV = 85.88% and TC = 99.59%	82
BiOBr/Cu ₂ O	TC degradation and Cr(vi) reduction	Degradation = 80.17 and 80.71% for TC and Cr(vi) within 100 min, respectively	83
BiOI/Cu ₂ O	CO ₂ photoreduction	CO and CH ₄ yields = 53.03 and 30.75 μmol m ⁻² , respectively, after 11 h	84
Cu ₂ O/Mn-doped CdS	H ₂ evolution	66.3 mmol g ⁻¹ h ⁻¹	85
Cu ₂ O/CdS	H ₂ evolution	12 366 μmol h ⁻¹ g ⁻¹	86
ReS ₂ /Cu ₂ O	CO ₂ photoreduction	CO yield of 14.3 μmol g ⁻¹ within 3 h	87
Cu ₂ O/g-C ₃ N ₄	TC degradation and Cr(vi) reduction	TC degradation = 95.1% and Cr(vi) reduction = 77.7% within 120 min	88
Cu ₂ O/g-C ₃ N ₄	CO ₂ photoreduction	CO and CH ₄ yield of 10.8 and 3.1 μmol g ⁻¹ h ⁻¹ , respectively	89
Cu ₂ O/g-C ₃ N ₄	H ₂ evolution and oxytetracycline hydrochloride (OTH) degradation	OTH removal of 94.8% after 120 min. H ₂ evolution rate = 552.6 μmol g ⁻¹ h ⁻¹	90
g-C ₃ N ₄ /Cu ₂ O	CO ₂ photoreduction and H ₂ O ₂ generation	CO and H ₂ O ₂ yield = 14.6 and 34.0 μmol mg ⁻¹ within 2 h	91
Cu ₂ O/CQDs	TC degradation	TC degradation = 92.49% within 100 min	92

establishing a strong interaction and mixing electronic states of individual components greatly improves charge carrier migration and their subsequent separation.

In particular, forming a continuous interface through a chemical bond dangling between the two components creates an accessible channel for barrier-less charge transfer.⁹⁴ In this vein, interfacial Cu(II)–O–Cu(I) bonding bridges are formed at the interface of Cu₂O and CuO, providing appropriate channels for photogenerated carrier transfer from CuO to Cu₂O in an S-scheme pathway.⁶⁵ The Cu(II)–O–Cu(I) bridge channels were constructed *via* an *in situ* reduction strategy. In this approach, preformed CuO nanosheets are partially reduced in a controllable manner by ascorbic acid and transformed into Cu₂O entities. Such interfacial bonding not only improves the thermodynamics of the CO₂-to-CO conversion process but also accelerates the reaction kinetics by altering the rate-determining step through modulation of the d-band center of the Cu(I) sites.

Favored by these interfacial bridges and the S-scheme mechanism, the optimized CuO/Cu₂O exhibited improved CO₂ photoreduction to CO with a conversion rate of 22.14 μmol g⁻¹ h⁻¹, which

is 43.5 and 15.4 times higher than that of pristine CuO and Cu₂O, respectively.⁶⁶

It seems that the *in situ* reduction strategy has promising potential for establishing strong interaction and electronic state mixing at the interface of individual components. Inspired by this technique, Cui and coworkers⁷⁴ deposited ultrafine Cu₂O NPs over different morphologies of W₁₈O₄₉ and used the composite photocatalysts for N₂ photoreduction. Cu₂O–W₁₈O₄₉ with ultrathin nanowire morphology exhibited the best NH₃ production rate of 252.4 μmol g⁻¹ h⁻¹, which is 11.8 times higher than that of the pristine W₁₈O₄₉. The strong interface bonding with abundant oxygen vacancies promotes the chemisorption and activation of N₂ molecules. Besides this attribute, the S-scheme heterojunction enhances the IEF and improves the separation and transfer of the photogenerated carriers, which were considered responsible for the observed activity enhancement.

It is clear that the integration of Cu₂O with metal oxide photocatalysts to construct S-scheme heterojunction photocatalysts not only promotes the charge separation at the interface



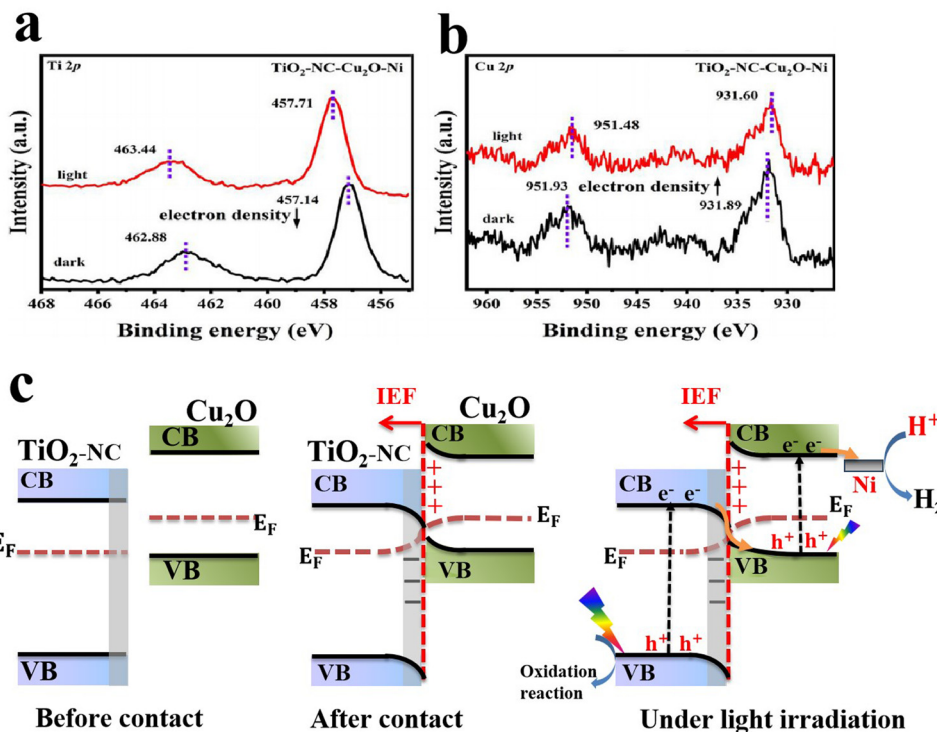


Fig. 16 (a) ISIXPS spectra of (c) Ti 2p and (b) Cu 2p for the TiO₂-NC-3%Cu₂O-3%Ni catalyst in the dark as well as under 365 nm light irradiation. Reproduced with permission.⁶⁸ Copyright 2024, Elsevier. (c) Schematic representation of interfacial electron transfer and migration over TiO₂-NC and Cu₂O before contact (left), after contact (middle), and under light irradiation (right).

and constrains the electron/hole pair recombination, but also boosts the reaction efficiency by maintaining useful charge carriers with maximum potential to trigger redox reactions and also alleviates the photo-corrosion issue of Cu₂O. In light of these studies, Cu₂O was chosen as the RP in the S-scheme heterojunction to avoid the accumulation of photogenerated holes within its VB, thus circumventing the photo-corrosion issue. Further loading of conductive cocatalysts and tailoring the interface with interfacial bonding has considerable potential to foster the charges' transfer and quench their recombination, thus enhancing the overall photocatalytic efficiency.

6.1.1.2. Cu₂O/binary metal oxide S-scheme heterojunctions.

Similar to metal oxides, Cu₂O can form S-heterojunctions with a wide range of binary metal oxides such as BiVO₄,⁷⁹ Bi₂WO₆,⁸⁰ and MgFe₂O₄,⁹⁵ etc. For instance, Huang *et al.*, synthesized single-crystal BiVO₄ with exposed (010) facets to achieve directional charge transfer and minimize bulk charge recombination. Subsequently, Cu₂O nanoparticles were grown by photodeposition technique along the (010) plane of BiVO₄ to construct an S-scheme heterojunction photocatalyst (Fig. 17a–c). MnOOH was loaded on the BiVO₄ (110) surface as a cocatalyst.⁷⁹ The best photocatalyst MnOOH/BiVO₄/Cu₂O exhibited the maximum H₂O₂ production performance of 112 μmol L⁻¹, *ca.* 3.5 times higher than that of BiVO₄/Cu₂O. However, the activity declined by 20% after the fifth recycling test. Since the work function of Cu₂O is smaller than that of BiVO₄, electrons flow from Cu₂O to BiVO₄ at the interface after contact. Therefore, an IEF is established at

the interface, in the direction from Cu₂O to BiVO₄ (Fig. 17d). Under light irradiation, photogenerated electrons and holes from BiVO₄ move selectively toward the (010) and (110) facets, respectively. The transferred electrons recombine with holes from Cu₂O. Meanwhile, photogenerated electrons at the Cu₂O CB and holes from BiVO₄ at the (110) facets effectively drive the overall H₂O₂ generation (Fig. 17d).

Delicate control over structural features such as facets, edges, and defects could open new pathways for further thwarting the unwanted charge carrier recombination. It is believed that these features could help establish a localized built-in electric field that boosts the charge separation process according to the S-scheme migration pathway. Careful consideration should be given to the stability issue of Cu₂O-based S-scheme photocatalysts.

6.1.1.3. Cu₂O/bismuth oxyhalide S-scheme heterojunctions.

Bismuth-based oxyhalides [BiO_mX_n] (X = F, Cl, Br, and I) represent a versatile category of layered structural materials with unique crystal and electronic structures, and exhibit interesting photocatalytic activity and stability. The layered crystal structure endows them with minimized electron–hole recombination and compositional flexibilities for bandgap tuning.⁹⁶ All these merits grant bismuth-based oxyhalide materials widespread usage in photocatalytic applications such as pollutant remediation, H₂ evolution, CO₂ reduction, and N₂ fixation.^{97–99} In this regard, Cu₂O has been used to construct S-scheme heterojunctions with different varieties of BiOX including BiOBr,^{81,82,100} BiOCl⁸³ and BiOI.⁸⁴



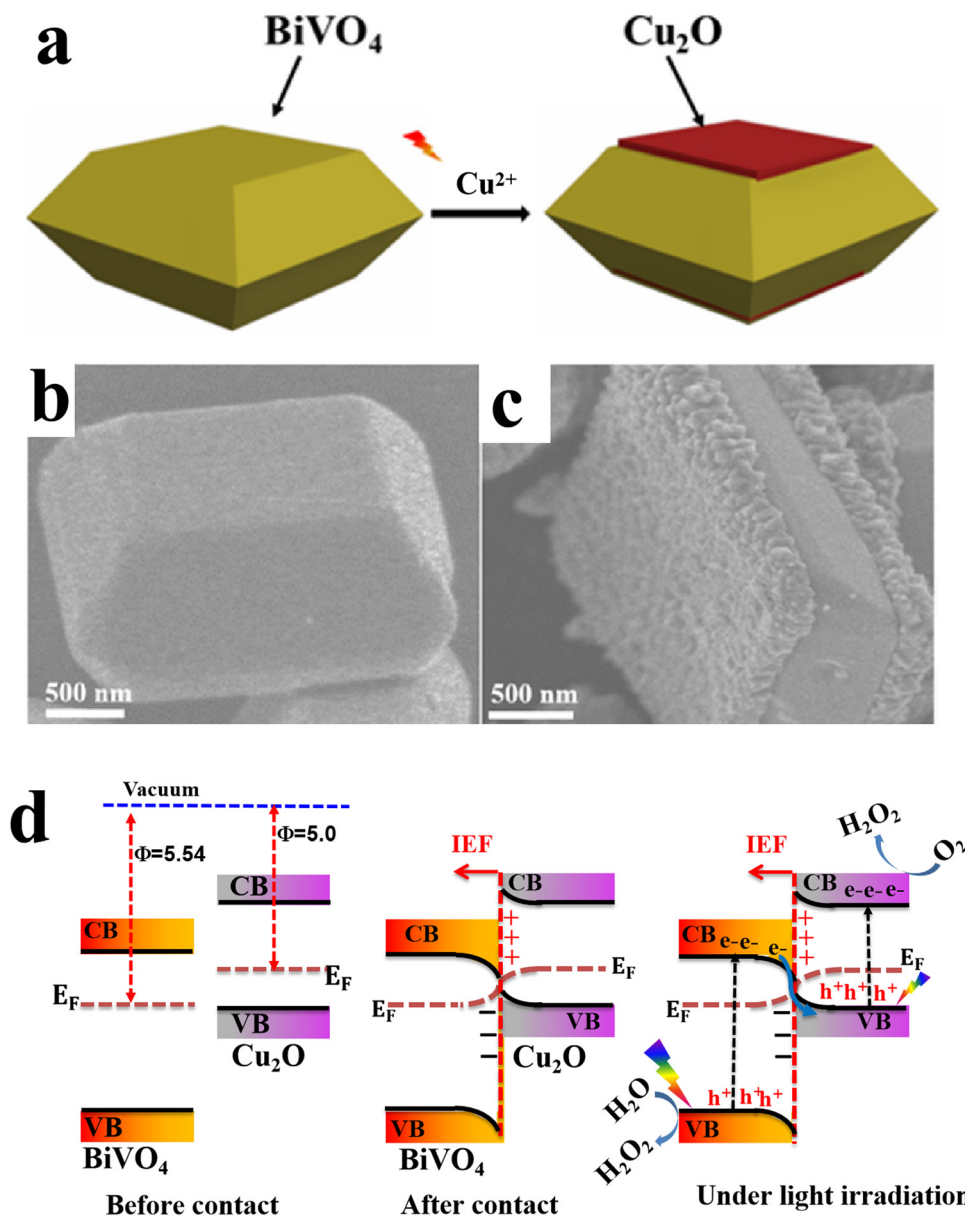


Fig. 17 (a) Scheme illustrating the preparation of the BiVO₄/Cu₂O S-scheme heterojunction. FESEM images of (b) BiVO₄ with exposed {010} and {110} facets and (c) BiVO₄/Cu₂O, where Cu₂O is grown selectively over the {010} facets. Reproduced with permission.⁷⁹ Copyright 2024, Royal Society of Chemistry. (d) Schematic illustration of the charge transfer mechanism over the BiVO₄/Cu₂O photocatalyst.

BiOX possesses a variable bandgap of ~ 3.3 eV for BiOCl, 2.7 eV for BiOBr, and 1.8 eV for BiOI.⁹⁸ Due to the anisotropic structural, optical, and electrical properties of BiOX materials, their semiconducting nature is dramatically affected by the composition, preparation method, starting precursor, and doping level. Therefore, they can exhibit p- or n-type semiconducting properties.^{96,98,101–106} Cu₂O can form S-scheme heterojunctions with BiOX photocatalysts regardless of their semiconducting nature, provided that the conditions for an S-scheme configuration are met, as shown in Fig. 8. For instance, Yan *et al.*,⁸¹ fabricated BiOBr/Cu₂O using a hydrothermal method for CO₂ photoreduction. The prepared composite samples showed moderate activity for CH₄ production with a selectivity of about 51%, while pure components produced CO only. The S-scheme configuration promotes the photogenerated electron–

hole separation, thus accumulating photogenerated electrons at the Cu₂O CB to trigger CO₂ reduction to CH₄ (8e⁻ per CH₄ molecule).

In another study, Gao and coworkers reported the fabrication and manipulation of BiOBr/Cu₂O S-scheme photocatalysts for various organic dye degradation processes.⁸² BiOBr nanosheets (NSs) were prepared using hydrothermal synthesis. Afterward, Cu₂O NPs were *in situ* generated over BiOBr NSs using typical alkali deposition followed by a reduction step. The composite photocatalyst, under the S-scheme mechanism operation, afforded high degradation efficiency for all targeted pollutants. Under light, photogenerated electrons in the BiOBr CB migrate to recombine with holes in the Cu₂O VB. Meanwhile, holes with a strong oxidation ability are located in the more positive position *i.e.* the VB of BiOBr, and are used directly to degrade



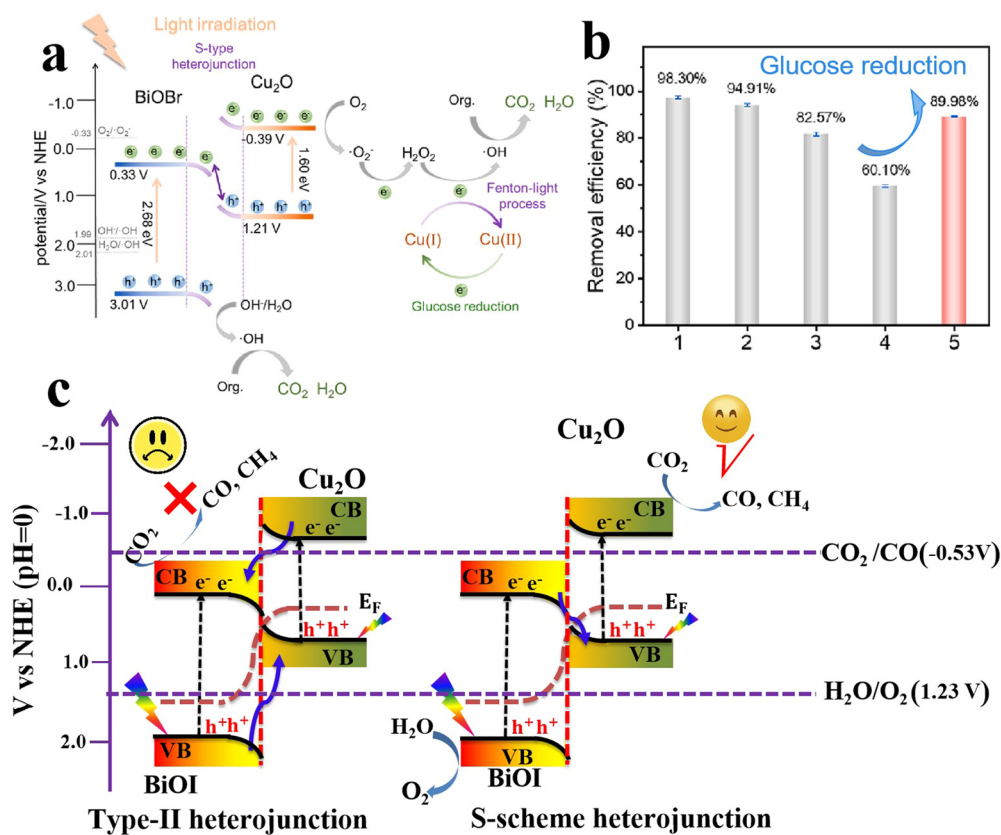


Fig. 18 (a) Schematic illustration of the synergism between a S-scheme heterojunction and a Fenton-like reaction over a Cu₂O/BiOBr photocatalyst. (b) The photocatalytic degradation efficiency of Cu₂O/BiOBr for MB decolorization after four cycles and glucose reduction. Reproduced with permission.⁸² Copyright 2023, Elsevier. (c) Comparison of type II heterojunctions (left) and the S-scheme mode (right) of photogenerated electron–hole migration in BiOI/Cu₂O composites.

organic contaminants or produce •OH from water oxidation. On the other hand, the electrons at the more negative position *i.e.* the CB of Cu₂O are consumed partially for O₂ reduction to H₂O₂ (Fig. 18a). Under these circumstances, Cu(I) plays an additional role in activating the conversion of produced H₂O₂ into •OH, *via* a Fenton-like process (Fig. 18a). Then, a portion of the photo-generated electrons at the Cu₂O CB are used to partially restore the initial Cu(I) species to sustain the S-scheme photocatalytic action. However, a 40% decrease in activity was observed after the fourth cycle of the recycling tests (Fig. 18b). When glucose was introduced into the system as a reducing agent, the activity was promoted from 60% to 90% (Fig. 18b). These results indicated that the photoreduction (without glucose) is not adequate to fully restore Cu(I). These findings highlight the role of Cu(I) species in activating a Fenton-like process and the possibility of integrating light-switching ionizable cocatalysts during photocatalytic processes. Further attempts to fully restore the Cu(I) species with the aid of the photogenerated charge carriers after a successful photocatalytic reaction without the need for external chemical reducing or oxidizing agents are highly encouraged. The effectiveness of Cu₂O/BiOX S-scheme photocatalysts has been again testified for the tetracycline degradation over BiOCl/Cu₂O.⁸³

Apart from particulate photocatalysts, Wang and coworkers synthesized polyhedral Cu₂O-modified BiOI NS thin film S-scheme photocatalysts over a fluorine-doped tin oxide substrate

via a stepwise electrodeposition technique and the supported Cu₂O/BiOI thin film used for CO₂ photoreduction.⁸⁴

The photocatalyst with optimal Cu₂O loading (BiOI/Cu₂O-1500, where 1500 refers to the electrodeposition cycles) exhibited improved CO₂ reduction ability, producing CO and CH₄ as the final reduction products, while oxygen was detected as an oxidation product. It was concluded that the S-scheme heterojunction formed at the BiOI/Cu₂O interface imparted the prepared catalyst with improved charge separation and photogenerated carriers with strong redox ability, which collaboratively led to enhanced photocatalytic performance. Specifically, the bandgaps (E_g) of the BiOI and Cu₂O samples were estimated to be 1.8 and 2.0 eV, respectively. The VB values of BiOI and Cu₂O were estimated to be 1.9 and 0.8 eV. Then, the CB positions of BiOI and Cu₂O were determined to be 0.1 and -1.2 V, respectively. Upon visible-light irradiation, according to the charge transfer principles of the S-scheme configuration, photogenerated electrons in the CB of BiOI will migrate under the influence of the IEF to recombine with holes within the Cu₂O VB.⁸⁴ Simultaneously, the accumulated electrons at the CB of Cu₂O with the reduction potential (-1.2 V vs. NHE), greater than the standard redox potential E° of CO₂/CO (-0.5 V vs. NHE) and E° of CO₂/CH₄ (-0.24 V vs. NHE), drive these half-reactions at varying rates (Fig. 18c). Meanwhile, O₂ production occurs *via* photogenerated holes at the VB edge of BiOI (1.9 V vs. NHE) as its oxidation potential exceeds the



standard redox potential for H₂O oxidation (O₂/H₂O = 1.23 V vs. NHE) (Fig. 18c-right). These results cannot be explained by a type-II heterojunction mechanism, as photogenerated electrons and holes would accumulate in the CB and VB of BiOI and Cu₂O, respectively, with reduction and oxidation potentials insufficient to achieve the targeted reactions (Fig. 18c-left).

6.1.1.4. Cu₂O/metal sulfide S-scheme heterojunctions. Metal sulfide (MS) photocatalysts have received enormous research interest due to their suitable band structure and promising photocatalytic performance. Compared to metal oxides, MS generally possesses a narrower bandgap and considerable visible light absorption ability.¹⁰⁷ CdS, MoS₂, Ag₂S, and Bi₂S₃ are among the most studied MS photocatalytic materials. However, the severe charge recombination and pronounced photo-corrosion hinder the efficiency of MS when used as a single-component photocatalyst, particularly CdS. Recently, transition-metal-substituted CdS solid solutions (M_xCd_{1-x}S) have been developed to enhance the photocatalytic performance of CdS, while diminishing the use of highly toxic Cd²⁺.^{85,94} Theoretically, the doped transition metal ions can induce spin-orbit coupling and hybridization with the electronic states of CdS, thereby shifting the CB position to more negative values, which favors reduction reactions such as H₂ evolution and CO₂ reduction. When combined with a suitable alternative to construct an S-scheme heterojunction, the resulting composite shows prospective catalytic efficiency. Based on these attributes, Fan *et al.*,⁸⁵ deposited Mn-doped CdS onto Cu₂O truncated octahedra *via* hydrothermal synthesis targeting photocatalytic H₂ evolution. The S-scheme Mn-doped CdS/Cu₂O photocatalyst exhibited outstanding H₂ evolution activity that is 3.4 and 55.3 times that of Mn-CdS and Cu₂O, respectively, and excellent stability during cycling. Upon Mn-doping, the CB of CdS shifted to a higher position, thereby promoting the H₂ evolution reaction, particularly after constructing the S-scheme heterojunction with Cu₂O.

MXenes have emerged as a rising star in the 2D materials arena and received considerable interest due to their unique physicochemical properties. In photocatalysis, MXene's excellent electrical conductivity and light absorption ability enable fast photogenerated charge carrier transfer and enhance photocatalytic conversion efficiency.^{108,109} When combined in an S-scheme heterojunction system, MXene can provide alternative charge transfer channels and abundant active sites, which are collectively essential for accelerating the photocatalytic reaction kinetics.^{86,110,111} Benefiting from these features, an S-scheme heterojunction system combining CdS and Ti₃C₂ MXene and coupled with Cu₂O was constructed for photocatalytic H₂ evolution reaction.⁸⁶ The synthesis route starts by CdS epitaxial and uniform growth on both surfaces of Ti₃C₂ MXene, followed by anchoring of NC-Cu₂O (Cu₂O@NC) (Fig. 19a). The synergistic effect of MXene and NC nanoparticles as conductive materials and cocatalysts endowed the MX-CdS-Cu₂O@NC structure with enhanced light absorption within the entire UV-vis range (Fig. 19b), thus powering their potential for efficient H₂ evolution. With these merits, the photocatalytic hydrogen evolution rate of the optimized 4%MX-CdS-7%Cu₂O@NC composite

reached a maximum of 12 366 μmol h⁻¹ g⁻¹, which is 7.4 times higher than that of pure CdS (Fig. 19c). The composite showed an 18.1% decrease in the H₂ evolution rate after six cycling tests compared to the initial rate (Fig. 19d). This decline in activity was mainly attributed to the photo-corrosion of Cu₂O and CdS. In this composite, Cu₂O and CdS were employed as OP and RP, respectively. Following the S-scheme configuration and under the IEF driving force, the photogenerated electrons from the Cu₂O CB recombine with holes at the CdS VB. Simultaneously, photogenerated electrons with the strongest reduction potential were utilized to trigger H₂ evolution efficiently. Meanwhile, photogenerated holes remaining at the Cu₂O VB participate in the oxidation reaction (Fig. 19e). These studies illustrate the potential of metal sulfides to construct effective S-scheme heterojunctions with Cu₂O. Integrating Cu₂O as the OP indeed raises its inherent photo-corrosion issue. Tailoring the surface of Cu₂O with an appropriate oxidation cocatalyst could alleviate the accumulation of photogenerated holes within the Cu₂O VB, thus improving its stability.

Rhenium disulfide (ReS₂) is a direct band gap semiconductor with excellent optical properties and has also been used to develop S-scheme photocatalytic systems with Cu₂O.¹¹² Cu₂O was derived from Cu foam by a thermal oxidation step followed by drop casting of previously prepared ReS₂. The resulting ReS₂@Cu₂O S-scheme photocatalyst exhibited improved CO₂ reduction activity with a CO yield of 14.3 μmol g⁻¹ under visible light irradiation and good stability. The obtained ReS₂ displayed an n-type semiconducting nature with a narrow bandgap of 1.55 eV and CB position at -0.22 V (vs. NHE). Meanwhile, Cu₂O with a bandgap of 1.8 eV and VB at 1.11 V (vs. NHE) showed p-type semiconducting characteristics. This combination realized an S-scheme configuration where ReS₂ and Cu₂O served as the OP and RP, respectively. The established IEF and the resulting S-scheme charge transfer pathway not only promoted the separation of the photogenerated charges but also enriched electrons with high reducing abilities in the Cu₂O CB, facilitating favorable CO₂ reduction and CO formation. Despite the improved performance, the scarcity and high cost of Re limit its wide integration for practical applications.

6.1.1.5. Cu₂O/carbon-based material S-scheme heterojunctions. Carbon-based photocatalytic and/or cocatalytic materials are among the most sustainable alternatives from the wise use of resources and economical viewpoints. With an exceptionally low bandgap, broad visible light absorption, easy functionalization, and low charge recombination, they can be developed as efficient substitutes for noble metal-based catalysts for photocatalytic applications.¹¹³⁻¹¹⁵ Graphitic carbon nitride (g-C₃N₄), graphene, QDs, and amorphous carbon are the most popular materials currently applied within the catalysis-related research arena. In this section, recent research on S-scheme heterojunctions composed of Cu₂O and the aforementioned carbon-based materials will be discussed.

6.1.1.5.1. Cu₂O/g-C₃N₄ S-scheme heterojunctions. g-C₃N₄ as a metal-free semiconductor with visible light response, suitable band structure and abundant availability, has drawn broad attention in photocatalysis, especially for solar energy conversion



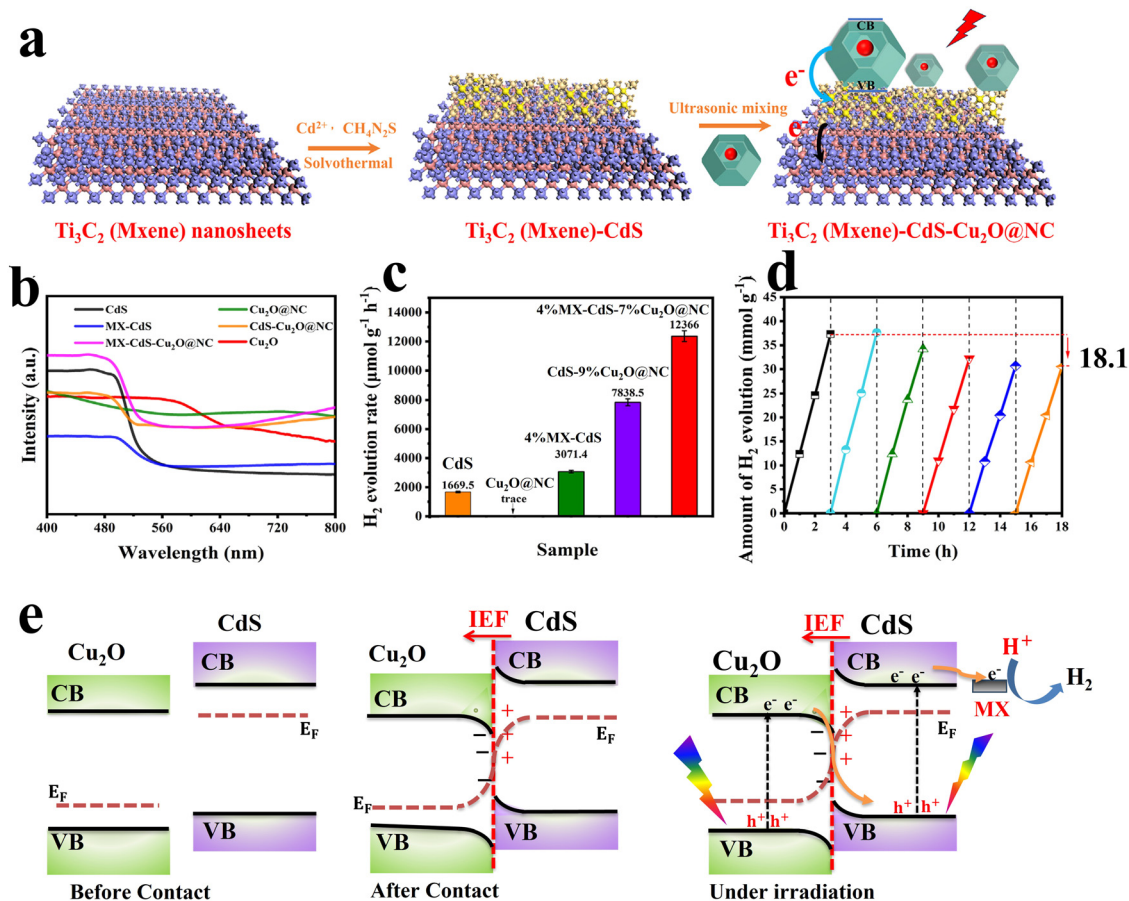



Fig. 19 (a) Schematic diagram showing the fabrication of MX-CdS- Cu_2O @NC composites; (b) UV-vis absorption spectra of different photocatalytic samples based on CdS and Cu_2O ; (c) hydrogen evolution of CdS, Cu_2O , 4%MXCdS, CdS-9% Cu_2O @NC and 4%MX-CdS-7% Cu_2O @NC; (d) photocatalytic hydrogen evolution upon reuse of 4%MX-CdS-7% Cu_2O @NC. Reproduced with permission.⁸⁶ Copyright 2023, Elsevier. (e) Schematic illustration of interfacial electron transfer at the interface between Cu_2O /CdS S-scheme heterojunctions.

and environmental remediation.^{116–118} Due to its remarkable features, $g\text{-C}_3\text{N}_4$ has been extensively used to date to construct S-scheme heterojunctions with organic and inorganic semiconductors.¹¹⁹ Regarding Cu_2O , multiple studies have examined the potential of $\text{Cu}_2\text{O}/g\text{-C}_3\text{N}_4$ S-scheme photocatalysts in different applications.^{120–123} The Zhao group fabricated a $\text{Cu}_2\text{O}/g\text{-C}_3\text{N}_4$ S-scheme heterojunction as a photocatalyst for degradation of a broad range of emerging pollutants in water, including TC, hexavalent Cr salt reduction, and H_2 evolution.¹²¹ Cu_2O octahedra were grown on $g\text{-C}_3\text{N}_4$ sheets *via* the well-adopted wet chemical reduction approach (Fig. 20a). The TC degradation efficiency of the optimized $\text{Cu}_2\text{O}/g\text{-C}_3\text{N}_4$ S-scheme heterojunction reached $\sim 100\%$ after 120 min (Fig. 20b). The authors determined the bandgap of the as-obtained Cu_2O and $g\text{-C}_3\text{N}_4$ to be 2.0 and 2.8 eV, respectively. Additionally, the VB edge of $g\text{-C}_3\text{N}_4$ and Cu_2O was determined to be 1.7 eV and 1.9 eV *vs.* NHE, respectively. Therefore, the CB positions of $g\text{-C}_3\text{N}_4$ and Cu_2O should be located at -1.1 eV and -0.1 eV *vs.* NHE, respectively. The free radical scavenging results showed that the dominant active species during TC degradation is the superoxide radicals $\bullet\text{O}_2^-$, yet photogenerated holes h^+ and hydroxyl radicals $\bullet\text{OH}$ both contribute to the overall efficiency, but to a lesser extent.

Based on these analyses and taking into account that the standard redox potential of $\text{O}_2/\bullet\text{O}_2^-$ (-0.3 eV *vs.* NHE, the main active species for TC degradation), the photogenerated electrons on the Cu_2O CB are not capable of producing $\bullet\text{O}_2^-$. Therefore, the type-II charge transfer mechanism cannot be used to explain the enhanced performance of the system (Fig. 20c, left). In this vein, the S-scheme mechanism can easily rationalize the experimental results (Fig. 20c, right). Under these circumstances, Cu_2O and $g\text{-C}_3\text{N}_4$ acted as the OP and RP, respectively. Photogenerated electrons at the $g\text{-C}_3\text{N}_4$ CB will be used up to accomplish H_2 evolution or Cr(vi) reduction, while the resultant holes at the Cu_2O VB will trigger TC degradation.¹²¹

When Cu plasmonic NPs were *in situ* generated over Cu_2O octahedron by controlled chemical reduction with NaBH_4 , the catalytic activity was further improved.¹²⁰ The obtained $g\text{-C}_3\text{N}_4/\text{Cu}_2\text{O}@Cu$ plasmonic S-scheme heterojunction displayed the highest CO and CH_4 generation rate, which is about 13.5 and 15.5 times higher than that of pristine Cu_2O , respectively. It is argued that the localized surface plasmon resonance (LSPR) of Cu NPs not only enhances light absorption by the composite but also promotes the generation and separation rate of photogenerated electron-hole pairs. Plasmonic Cu NPs can act as



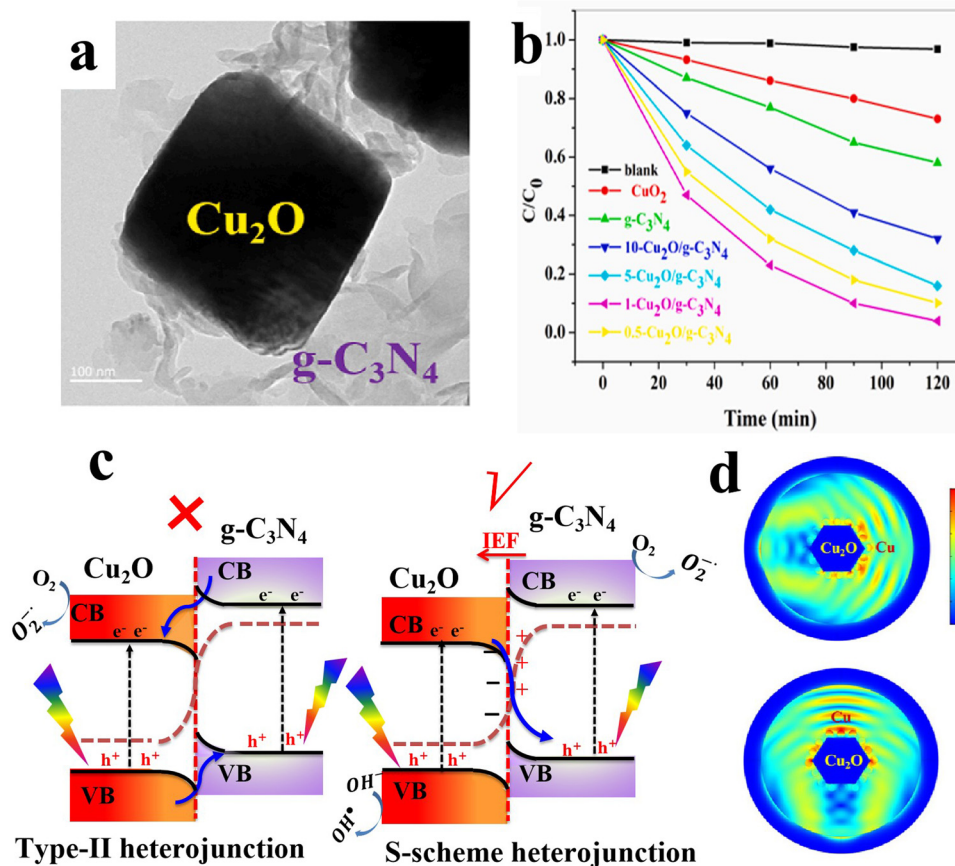


Fig. 20 (a) TEM of Cu₂O/g-C₃N₄; (b) photocatalytic activity of different prepared samples for TC degradation. Reproduced with permission.¹²¹ Copyright 2022, Elsevier. (c) The proposed type-II staggered band alignment (left) and S-scheme mechanism over the Cu₂O/g-C₃N₄ heterojunction photocatalyst (right). (d) Finite-difference time-domain simulation of the two-dimension cross-section of the Cu₂O@Cu structure. The light is irradiated from the side (upper) and top (lower) of the section, respectively. Reproduced with permission.¹²⁰ Copyright 2022, Elsevier.

hotspots to maximize the intensity of the local electric field, thus enhancing the generation ability of electron-hole pairs nearby (Fig. 20d). Similar functionality attributes and plasmonic-based enhancements were reported for Au NPs anchored on the g-C₃N₄/Cu₂O S-scheme heterojunction employed for H₂ evolution and OTH degradation.⁹⁰

It is worth mentioning that changing the preparation method can significantly alter the structural, optical, and electronic properties of a given semiconductor. Wei *et al.*,⁹¹ fabricated a g-C₃N₄/Cu₂O-Pd S-scheme heterojunction using the well-documented *in situ* deposition method. However, the g-C₃N₄ was obtained by double calcination of a mixed melamine-urea precursor. The obtained heterostructure showed outstanding activity for H₂O oxidation to H₂O₂ and CO₂ reduction to CO. Unlike previous studies that focused on g-C₃N₄/Cu₂O S-scheme photocatalysts, the obtained g-C₃N₄ had a CB position relatively lower than pristine Cu₂O. Therefore, in this g-C₃N₄/Cu₂O junction, g-C₃N₄ served as the OP, while Cu₂O with a higher CB position functioned as the RP. This configuration synergistically promoted directional photogenerated charge separation and improved Cu₂O stability, as it prevents the accumulation of holes at the Cu₂O VB. After four consecutive uses, the g-C₃N₄/Cu₂O-Pd heterojunction showed a stable

photocatalytic activity, suggesting its stability and reusability. Future studies should carefully consider the stability issue of Cu₂O by deliberately designing and integrating Cu₂O as the RP in combination with a suitable OP, to ensure adequate protection after the transfer of photogenerated holes from the Cu₂O VB during S-scheme charge separation.

6.1.1.5.2. Cu₂O/CQD S-scheme heterojunctions. Due to their diverse physicochemical properties and favorable attributes, CQDs and their derived hybrids have shown promising prospects in the energy conversion and storage fields.¹²⁴ Occasionally, carbon-based materials can be derived from bio-waste, thereby implementing a sustainable process while valorizing useless wastes. Derived from corn stover by a hydrothermal alkali treatment, CQDs were obtained and combined with Cu₂O dodecahedrons.⁹² The prepared CQD/Cu₂O S-scheme photocatalyst afforded enhanced TC degradation activity and outstanding stability during the cycling test. The incorporation of CQDs enhanced both the visible light absorption and the separation of electron-hole pairs. The stability of Cu₂O as the OP remains debatable. In this regard, it is proposed that carbonaceous materials can provide local protection against oxidation of Cu₂O,¹²⁵ if photogenerated charge carriers transfer efficiently



within the S-scheme heterojunction systems. However, experimental evidence is needed to support Cu₂O stability, there being still significant room for exploration regarding the integration of Cu₂O with C-based materials to construct efficient S-scheme photocatalysts.

6.1.1.6. Cu₂O/MOF and Cu₂O/MOF derivative S-scheme heterojunctions. MOFs are a class of crystalline porous materials composed of organic ligands coordinated to metal centers.^{126,127} Due to their extremely large surface area, high and tailored porosity, and tunable optical and electronic characteristics, MOFs are extensively studied as photo- and/or co-catalytic scaffolds.^{128–130} Combining MOFs with suitable semiconducting materials can result in MOF-based S-scheme heterojunctions in which the advantages of MOFs are maintained and photogenerated charge carriers undergo migration according to the S-scheme mechanism.^{130,131} Cu₂O has been combined with various MOFs and their derivatives and tested for pollutant degradation,^{132,133} H₂ evolution,¹³⁴ CO₂ reduction^{135,136} and organic synthesis.¹³⁷

Multiple compositions with various optical and electronic properties could be attained by design. For instance, MOFs with desirable electronic features (lowest unoccupied molecular orbital (LUMO) and highest occupied molecular orbitals (HOMO)) and organic linkers with different functionalities can be combined with Cu₂O to construct S-scheme heterojunctions with adequate activity, selectivity, and pronounced stability during targeted photocatalytic reactions. Moreover, MOFs can grow on different shapes of Cu₂O with different exposed facets, thereby dramatically altering the optical and electronic properties.¹³²

Controlled calcination of Cu-based MOFs can be used to prepare different heterojunctions according to the temperature and the calcination environment.^{134,137} For example, Cu₂O@NC yolk-shell cuboctahedrons were synthesized *via* the calcination of Cu-BTC MOF (HKUST; btc = benzene-1,3,5-tricarboxylate) at 300 °C for 30 min under an Ar atmosphere. The prepared Cu₂O@NC hollow structures showed great potential for the cross-dehydrogenative coupling (C–C bond formation) reaction of tetrahydroisoquinoline and indole. The improved activity was attributed to the prolonged lifetime of photogenerated charge carriers after separation at the interface, to multiple reflections of light by the yolk-shell hollow structure favoring light absorption, and improved stability upon heterojunction formation.¹³⁷ Alternately, P-doped carbon/Cu₂O heterostructures could be obtained by the calcination of triphenylphosphine-modified Cu-BTC MOFs.¹³⁴

When the Cu₂O structure is immersed in a solution containing BTC ligand, spontaneous *in situ* etching of Cu₂O and coordination of Cu ions with BTC organic linkers results in the spontaneous appearance of an HKUST MOF shell, forming core-shell Cu₂O@HKUST.^{136,138} The formation of HKUST MOF shell over the Cu₂O core not only suppressed the water-induced corrosion of Cu₂O during CO₂ photoreduction or TC degradation reactions but also facilitated photogenerated charges separation and reactant uptake. This resulted in nanocomposites with improved activity and stability for selective photocatalytic CO₂ reduction into CH₄ and TC degradation.^{136,138}

These studies highlight the diverse opportunities for designing S-scheme heterojunctions from Cu₂O@MOFs and/or their derivatives. The composition, morphology, optical, and electronic properties of the targeted composites can be deliberately tuned based on the unique flexibility and vast functionalities offered by MOFs. Importantly, Cu₂O@MOF core-shell or yolk-shell structures have proven profound long-term stability under operating conditions and thus can overcome the corrosion issue of Cu₂O photocatalysts. Despite these merits, research studies on Cu₂O@MOF S-scheme photocatalytic systems are still scarce.

6.1.1.7. Other Cu₂O-based S-scheme heterojunctions. Apart from the well-known photocatalytic materials applied so far to construct heterojunctions, Cu₂O can form S-scheme photocatalysts with alternative materials such as multicomponent hydroxides,¹³⁹ Cu₄(SO₄)(OH)₆¹⁴⁰ and CsPbBr₃ perovskite nanocrystals.¹⁴¹ Perovskite nanocrystals and layered double hydroxides (LDHs) are versatile families of inorganic materials with exceptional optoelectronic properties, customizable composition, and diverse catalytic functionalities. Owing to these merits, they have garnered significant research interest for their manipulation in photocatalytic applications.^{142–144} Combining the unique advantages of perovskite nanocrystals or LDH materials with tailored composition and optoelectronic features with Cu₂O can result in efficient S-scheme heterojunctions with desirable activity, selectivity, and stability.

6.1.2. CuO. CuO is a crystallographic variant of copper-based oxides. Its monoclinic phase structure is more thermostable than the cubic Cu₂O counterpart.¹⁴⁵ CuO is a p-type semiconductor with a bandgap of 1.2–2.0 eV depending largely on the synthesis method, appropriate redox potential, and excellent stability in aqueous solutions.¹⁴⁶ These features make a wide integration of CuO in photocatalytic applications possible.^{147–150} CuO is used extensively to construct S-scheme heterojunctions with different photocatalytic materials, including metal oxides, metal sulfides, and g-C₃N₄. Table 4 displays the most studied S-scheme heterojunctions based on CuO for various applications. The next sections will discuss recent progress and advancements in CuO-based S-scheme photocatalytic systems.

6.1.2.1. CuO/metal oxide S-scheme heterojunctions. Different metal oxide photocatalysts have been combined so far with CuO to construct S-scheme heterojunctions including Cu₂O,^{165,166} TiO₂,¹⁴⁶ ZnO,^{149–153,167} WO₃,¹⁵⁶ CdO,¹⁵⁵ NiO,¹⁶⁸ In₂O₃,¹⁴⁷ ZrO₂¹⁶⁹ and CeO₂.¹⁵⁴ In this regard, CuO-based S-scheme heterojunctions with metal oxides were fabricated based on different approaches including the sol-gel technique followed by calcination in air,^{153,154,169} MOFs-derived method,^{147,150} and solid-state mixing.¹⁴⁶ Of them, the MOF-based approach shows particular promise as the obtained photocatalysts may partially retain the precursor porosity, inheriting them with abundant active sites, higher light absorption, minimized charge carrier recombination, and feasible mass and/or charge transfer.¹⁵⁰

In this vein, a CuO/ZnO S-scheme heterojunction was directly formed by calcination of Cu-rich ZIF-8. HRTEM and XRD results confirmed the formation of the CuO phase alongside the wurtzite phase ZnO. The nanocomposite with optimum CuO



Table 4 S-scheme photocatalytic systems based on CuO with various photocatalytic materials reported for diverse applications. The S-scheme heterojunctions are arranged as OP/RP

S-scheme heterojunction	Application	Efficiency	Ref.
ZnO/CuO	MB dye degradation	~ 100% degradation in 10 min	150
ZnO/CuO	Rhodamine 6G (R6G)	~ 85% degradation in 5 h	149
ZnO/CuO	H ₂ evolution	The H ₂ evolution rate of 4655 $\mu\text{mol g}^{-1} \text{h}^{-1}$	151
ZnO/CuO	H ₂ evolution	The H ₂ evolution rate of 37.2 $\text{mmol g}^{-1} \text{h}^{-1}$	152
ZnO/CuO	Hg(II) reduction	100% photoreduction within 60 min	153
CuO/In ₂ O ₃	CO ₂ reduction	CH ₄ and CO yields of 190.32 $\mu\text{mol g}^{-1} \text{h}^{-1}$ and 500.46 $\mu\text{mol g}^{-1} \text{h}^{-1}$, respectively	147
TiO ₂ /CuO	Degradation of acid red 8 dye (AR8)	~ 90% degradation in 50 min	146
CeO ₂ /CuO	Atrazine (AT) degradation	100% degradation within 50 min	154
CuO/CdO	Levofloxacin (LVF) degradation	96.11% degradation of LVF after 30 min	155
WO ₃ /CuO	Cr(VI) reduction	100% Cr(VI) reduction after 30 min	156
BiVO ₄ /CuO	NOR degradation	95.1% degradation of NOR after 60 min	148
CuO/ZnFe ₂ O ₄	MG degradation	95% degradation of MG in 90 min	157
CuO/CuBi ₂ O ₄	CO ₂ reduction	CO and CH ₄ yields within 9 h of 1599.1 and 5.1 $\mu\text{mol m}^{-2}$, respectively	158
CuO/ZnIn ₂ S ₄	CO ₂ reduction	CO yield = 6.9 $\mu\text{mol g}^{-1} \text{h}^{-1}$ CH ₄ yield = 54.4 $\mu\text{mol g}^{-1} \text{h}^{-1}$	159
CuO/Bi ₂ S ₃	CO ₂ reduction	CH ₃ OH and HCOOH yields of 423.5 and 17.5 $\mu\text{mol g}^{-1} \text{h}^{-1}$, respectively	160
CuO/g-C ₃ N ₄	TC degradation	95% degradation of TC in 2 h	161
CuO/g-C ₃ N ₄	Xanthate degradation	83.2% degradation of xanthate in 1 h	162
CuO/g-C ₃ N ₄	H ₂ evolution	3848 $\mu\text{mol g}^{-1}$ in 8 h	163
InP/CuO	CIP degradation	81.7% degradation of CIP after 15 min	164

loading exhibited fast degradation kinetics for different targeted pollutants including MB and RhB dyes, bisphenol A (BPA), and TC in the presence of peroxymonosulfate (PMS).¹⁵⁰ The excellent activity was primarily attributed to the enhanced visible light absorption and the synergistic role of Cu and Zn species for PMS adsorption and activation. After light illumination, photogenerated electrons and holes at the CuO CB and ZnO VB, respectively, were maintained to trigger the redox generation of active species. Cu²⁺/Cu⁺ pairs play a key role as ionizable cocatalysts during free radical formation.

In a recent study, a MOF-on-MOF interfacial engineering strategy was adopted to fabricate an In₂O₃ nanosheet-wrapped CuO core-shell structure (CuO@In₂O₃) S-scheme heterojunction for efficient photocatalytic CO₂ reduction (Fig. 21).¹⁴⁷ Cu-HKUST MOFs with octahedral morphology were first fabricated. Then, In-MOF nanosheets were grown at the outer surfaces of Cu-MOF octahedrons (Fig. 21a and b). Upon calcination in an air atmosphere, the MOF-on-MOF structure transformed into a CuO@In₂O₃ core-shell composite with an almost identical shape to the original precursor (Fig. 21b). The CuO@In₂O₃ heterostructure was proven to have excellent CO₂ reduction activity *ca.* CH₄ and CO yields of 190.32 $\mu\text{mol g}^{-1} \text{h}^{-1}$ and 500.46 $\mu\text{mol g}^{-1} \text{h}^{-1}$, almost 2.1 and 10.3 times and 2.4 and 7.9 times higher than that of pristine CuO and In₂O₃, respectively (Fig. 21c). The bandgap and VB position values of CuO and In₂O₃ were calculated to be 1.98 and 2.86 eV, and 1.62 and 1.22 eV, respectively. Based on this analysis, the authors proposed the charge separation mechanism as displayed in Fig. 21d. In₂O₃ is an n-type semiconductor with a Fermi level and CB position higher than those of the p-type CuO. Therefore, CuO and In₂O₃ functioned as the OP and RP in this configuration. Under light irradiation, electrons with lesser reduction potential at the CuO CB recombine with holes of lower oxidation potential at the In₂O₃ VB, while photogenerated electrons and holes with the highest reduction and oxidation power are maintained preferentially at the In₂O₃ CB and CuO VB, respectively.

This S-scheme charge transfer mechanism, along with the enhanced light absorption, improved CO₂ adsorption, and the large density of exposed active sites of the nanocomposites compared to the pristine components, were all responsible for the activity enhancement. These studies exemplify the effectiveness of the MOF-based strategy for customizable CuO-based S-scheme heterojunctions with desirable features and excellent performance.

As mentioned before, conductive materials, metallic species, and other co-catalytic scaffolds are widely integrated within S-scheme heterojunctions to boost the charge transfer process and enhance the overall activity. For example, when plasmonic Ag NPs are deposited over the ZnO/CuO system using DC magnetron sputtering, the photocatalytic degradation activity for rhodamine 6G (R6G) was drastically enhanced.¹⁴⁹ CuO and ZnO are typical p- and n-type semiconductors, respectively, with staggered band positions that can form an S-scheme configuration with ZnO as the OP and CuO as the RP. Hot electrons are generated within Ag NPs due to LSPR excitation. Under these conditions, a double built-in electric field was established at the Ag-ZnO and ZnO-CuO interfaces. The double field prevents the recombination of electrons from Ag and the CuO CB with the holes in the VB of ZnO that are proposed to be responsible for the observed photocatalytic activity. Thus, full use of photogenerated electrons at Ag and CuO became possible, favoring improved activity. Similarly, Au NPs can also be used to enhance the visible light absorption of the CuO-ZnO S-scheme hybrid due to its LSPR band at about 560 nm.¹⁵¹

The integration of an S-scheme heterojunction with plasmonic metal NPs is a valid approach to satisfactorily promote the overall performance of the system. Notably, non-noble plasmonic metals are promising alternatives due to their earth abundance, tunable features, and feasible manipulation of their LSPR response beyond the visible range.^{50,170}

In addition to metallic species, non-metallic entities offer substantial potential for catalytic applications. In this regard



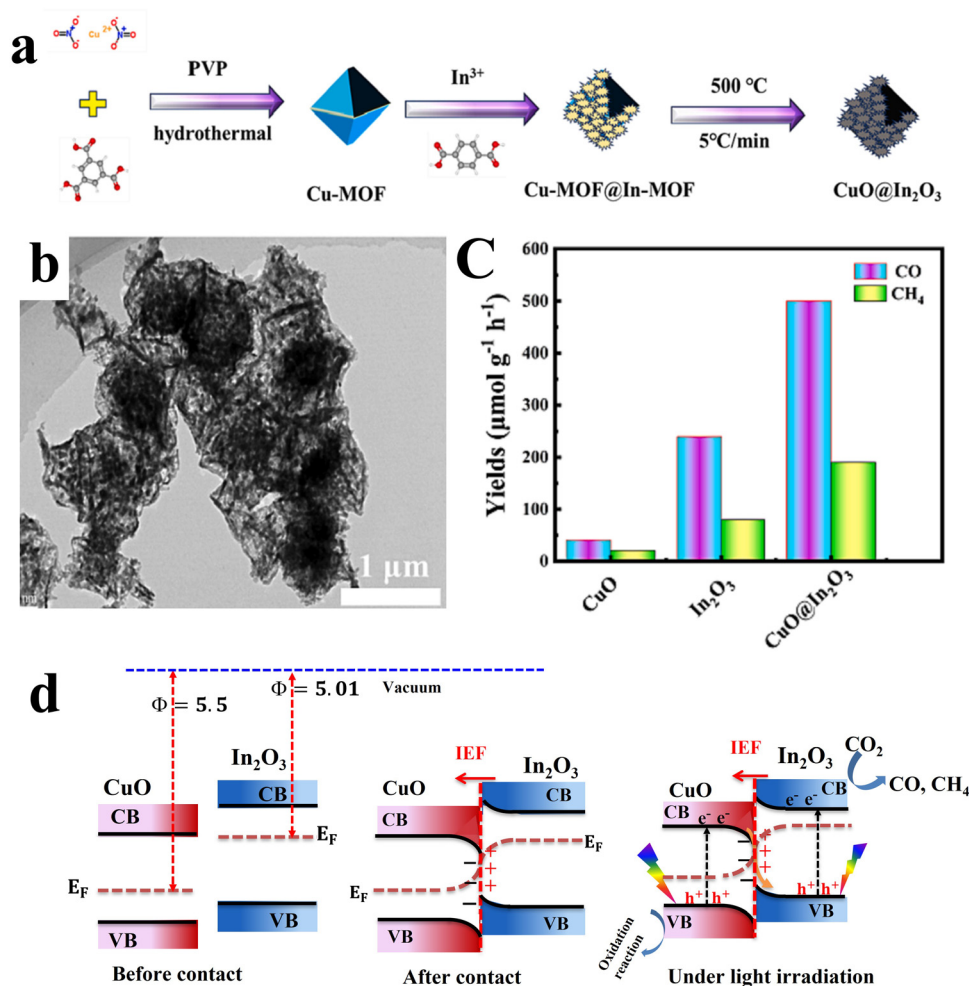


Fig. 21 (a) Schematic of the synthesis of CuO@In₂O₃ composites; (b) TEM images of CuO@In₂O₃ composites; (c) production rates of CO and CH₄ production over the studied photocatalysts. Reproduced with permission.¹⁴⁷ Copyright 2023, Elsevier. (d) Schematic layout of the band structure of the CuO/In₂O₃ S-scheme heterojunction and proposed charge transfer dynamics and reaction mechanism.

and due to the excellent electrical conductivity of graphene, it is extensively employed as a support/cocatalyst in photocatalytic and electrocatalytic applications.¹⁷¹ When ZnO and CuO were anchored on graphene, the system displayed the highest H₂ production rate of 37.2 mmol g⁻¹ h⁻¹, which was 3.3 times higher than pristine CuO/ZnO alone.¹⁵² In this configuration, graphene further boosted the S-scheme charge transfer owing to its unique electrical conductivity favoring the transport of photoexcited electrons between the semiconductors.

Other carbon-based scaffolds such as carbon nanotubes (CNTs) and CQDs can exhibit similar functions. Recently, graphdiyne (GDY), a rising star of 2D carbon allotropes, has demonstrated excellent charge carrier transfer efficiency and high conductivity.¹⁷² These features make GDY a leading candidate in photo- and electro-catalytic applications.^{173,174} Future studies are encouraged to elaborate on the role of GDY as a cocatalyst in combination with Cu-based S-scheme photocatalytic systems. Carbon-based materials can be used as active cocatalysts to boost the S-scheme charge migration and separation, improving activity and/or modifying the selectivity of the photocatalytic reaction.

The studies discussed in this section provide a clear picture of CuO/metal oxide-based S-scheme photocatalysts. CuO-based S-scheme systems with metal oxide semiconductors showed improved activity and better stability over their Cu₂O-based counterparts.^{146,154} In conclusion, CuO can serve as the RP or OP in S-scheme systems due to its suitable band positions and good stability. Partial reduction of Cu(II) to Cu(I) during the photocatalytic process can enhance the efficiency as the redox pair can act as an ionizable cocatalyst. Careful consideration is needed during bandgap measurements, Fermi level analysis, and band position determination to allow appropriate justification of the S-scheme heterojunction configuration.

6.1.2.2. CuO/binary metal oxide S-scheme heterojunctions. CuO has considerable potential in pollutant degradation through Fenton-like and PMS-based advanced oxidation processes. In this vein, Cu²⁺/Cu⁺ redox pairs act as active sites for the activation and generation of reactive species by swinging between the two redox states while transferring one electron to H₂O₂ or PMS.^{175,176} The initial Cu²⁺ can be restored during the



reaction course by the photogenerated hole to sustain the activity of the photocatalyst. It is found that the $\text{Cu}^+/\text{Cu}^{2+}$ redox pair acts as an activator in Fenton-like pollutant degradation processes. Its role has also been proposed in other redox reactions such as CO_2 reduction and H_2O_2 generation.

Since CuO activity is limited by the recombination rate of photogenerated electron-hole pairs, it is highly desirable to integrate CuO in S-scheme systems to mitigate the limitation derived from this favorable charge recombination and promote the photocatalytic degradation activity of the system.^{148,157} Bismuth vanadate (BiVO_4) is an example of a binary metal oxide with high oxidation potential, thus acting as the OP in S-scheme photocatalytic systems. With the potential to tailor the exposed

facets, surface homojunction formation between $\{010\}$ and $\{110\}$ planes of BiVO_4 is possible. Typically, when BiVO_4 is excited with suitable light, electrons are transferred to the $\{010\}$ facets and holes are accumulated on the $\{110\}$ facets.^{177,178} In this regard, when CuO is deposited over the $\{010\}$ facets of BiVO_4 , an S-scheme heterojunction is established at the interface (Fig. 22a, b and e), both BiVO_4 facets drive electrons to CuO, thereby accelerating the $\text{Cu}^{2+}/\text{Cu}^+$ cycle and enabling efficient PMS activation, all of which contribute to system activity, stability, and durability (Fig. 22c and d).¹⁴⁸ Photogenerated holes that accumulated at the $\{110\}$ facets would be consumed for PMS activation as well (Fig. 22e). Inspired by this synergism of charge separation, the CuO/BiVO_4 S-scheme photocatalysts exhibited

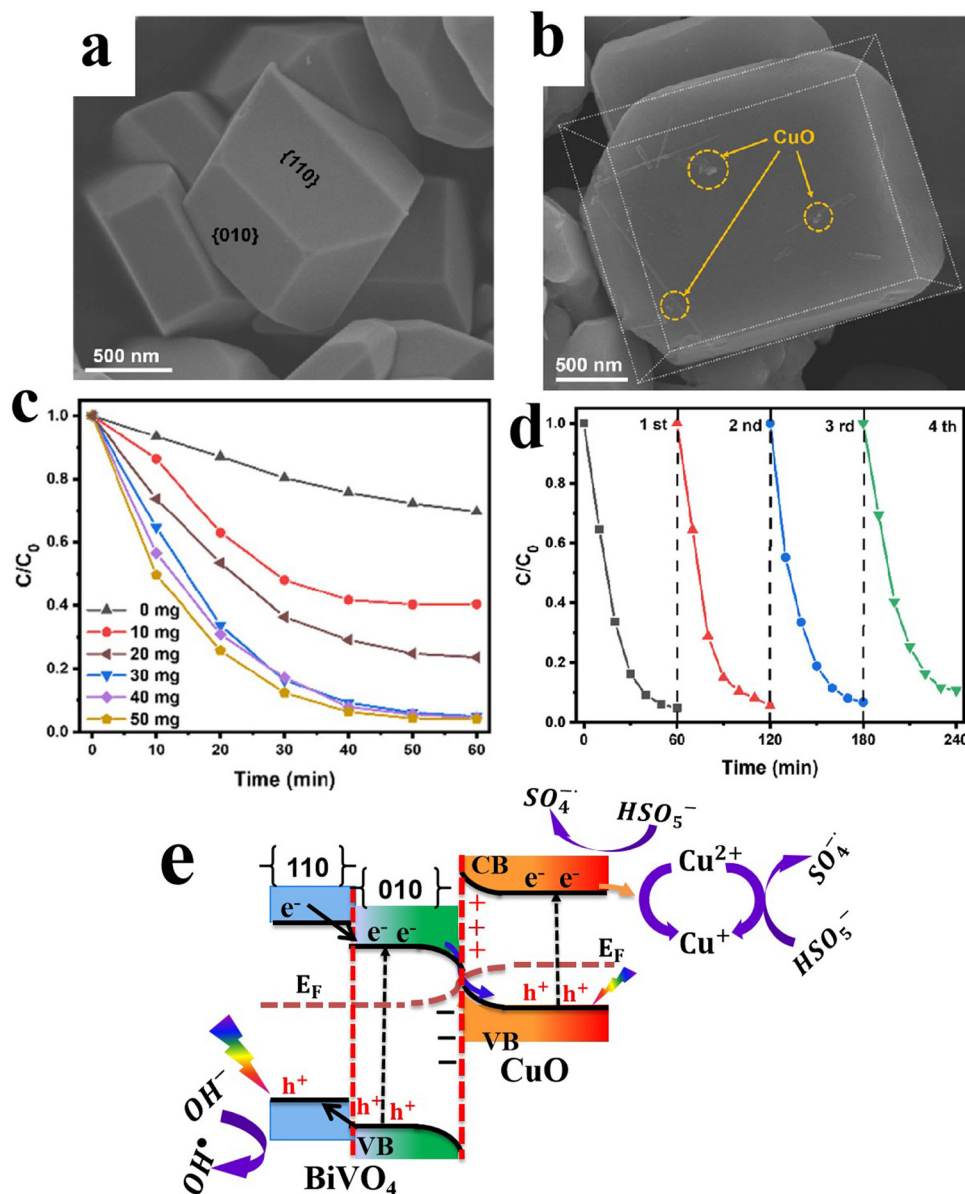


Fig. 22 FESEM images of (a) BiVO_4 and (b) CuO/BiVO_4 samples, highlighting the location of CuO NPs. (c) Photocatalytic degradation efficiency of CuO/BiVO_4 for the NOR solution at different PMS doses and (d) the recyclability of the CuO/BiVO_4 photocatalyst. Reproduced with permission.¹⁴⁸ Copyright 2024, Elsevier. (e) Proposed mechanism of NOR degradation over the $\text{CuO}/\text{BiVO}_4/\text{PMS}$ system.



excellent norfloxacin (NOR) degradation efficiency of 95.1% within 60 min in the presence of PMS (Fig. 22c), which was 3.65 and 2.45 times that of CuO and BiVO₄, and pronounced stability over four recycling cycles (Fig. 22d).

ZnFe₂O₄ and CuBi₂O₄ are among the binary metal oxides that have been reported forming S-scheme photocatalytic systems with CuO.^{157,158} Of these, ZnFe₂O₄ and CuO were uniformly immobilized on the surface of 2D BiOBr nanoplates to build a dual S-scheme configuration, which not only steered the charge migration to desirable positions, but also endowed the system with ultimate robustness.¹⁵⁷ Significantly, the ternary S-scheme heterojunctions attained optimum photocatalytic malachite green (MG) degradation efficiency of 95% in 90 min and *ca.* 6.57, 3.78, and 4.31 times faster reaction kinetics compared to BiOBr, ZnFe₂O₄, and CuO, respectively. Despite the potential of the resultant S-scheme photocatalysts after the combination of binary metal oxides with CuO, the number of studies in this area remains limited.

6.1.2.3. CuO/metal sulfide S-scheme heterojunctions. Metal sulfides (MS) have attracted attention as suitable semiconductors to form S-scheme heterojunctions with CuO due to their excellent visible light absorption capability and high reduction potential.^{179–181} After being integrated into an S-scheme system, the activity and selectivity of the resulting CuO heterojunctions were optimized, and the stability issue of MS was effectively addressed. MS functions as a RP when integrated with CuO in an S-scheme configuration, thus photogenerated holes on their VBs are recombined with photogenerated electrons from CuO under the influence of IEF. In light of these peculiar enhancements, the CuO@ZnIn₂S₄ heterojunction was constructed by a hydrothermal method and applied for CO₂ photoreduction.¹⁵⁹ Ag NPs were introduced onto CuO@ZnIn₂S₄ by photodeposition. The heterostructure components interact strongly, and an interfacial Cu–S bond was formed at the interface, as evidenced by the XPS results of the S 2p spectrum (Fig. 23a). Upon this strong interaction and the formation of a new charge transfer channel, *i.e.*, Cu–S bonds, the charges were redistributed at the interface, and electrons moved from ZnIn₂S₄ to CuO. This charge transfer induced a partial reduction of Cu(II) in CuO to Cu(I) after combination with ZnIn₂S₄ (Fig. 23b). The reduction extent further increased after the deposition of plasmonic Ag NPs, as Ag possesses a higher Fermi energy level, and electrons can flow from Ag to CuO to form a metal/semiconductor junction. The charge distribution and transfer at the interface were further confirmed through charge density difference calculations using DFT theoretical simulations (Fig. 23c). After combining ZnIn₂S₄ and CuO, regions of charge depletion and accumulation were formed at ZnIn₂S₄ and CuO, respectively, indicating electron transfer from ZnIn₂S₄ to CuO (Fig. 23d). Under light irradiation, the charge transfer direction reversed and photogenerated electrons at the CuO CB moved to recombine with holes on the ZnIn₂S₄ VB. Meanwhile, electrons and holes with the highest redox potential at ZnIn₂S₄ and CuO, respectively, are maintained to initiate CO₂ reduction and oxidation reactions (Fig. 23e). The remarkable catalytic activity and selectivity observed for CO₂ reduction were

assigned to three factors: (i) the S-scheme charge transfer mechanism operating for CuO@ZnIn₂S₄, driving the charge separation at the interface, (ii) the emergence of Cu–S covalent bonds that open an additional channel for accelerated charge carrier migration, and (iii) Ag NPs exploited its LSPR effect and enhanced the product selectivity by controlling the reaction intermediate.¹⁵⁹

In other example, reduced graphene oxide (r-GO) was used as a cocatalyst of the CuO/Bi₂S₃ S-scheme photocatalyst. The synthesized nanocomposite exhibited the maximum CO₂ reduction activity with a methanol yield of 423.52 μmol g^{−1} h^{−1} and the selectivity approached 99%.¹⁶⁰ These studies provide a useful approach to constructing S-scheme heterojunction systems based on CuO/MS in combination with effective cocatalysts for tuning product selectivity, promoting catalytic activity, and enhancing the stability of the system. CdS, stoichiometric ZnCdS, and other MS are plausible alternatives for future studies.

6.1.2.4. CuO/g-C₃N₄ S-scheme heterojunction. CuO in combination with g-C₃N₄ can form an S-scheme heterojunction in which CuO and g-C₃N₄ will function as the OP and RP, respectively. In a recent study, Wang and her group developed a fascinating strategy to extract Cu ions from solid wastes using an acid-leaching approach.¹⁶¹ After being extracted, Cu ions were mixed with a definite amount of melamine and cyanuric acid as g-C₃N₄ precursors, and the final macromolecular polymer was subjected to calcination in air at 550 °C to yield CuO/g-C₃N₄ nanocomposites. When tested for TC photocatalytic degradation, the CuO/C₃N₄ S-scheme heterojunction exhibited 95% degradation efficiency after 2 h with *ca.* 45% mineralization. After the S-scheme charge transfer mechanism came into action, photogenerated electrons and holes with the strongest reduction and oxidation potentials were preserved at C₃N₄ and CuO, respectively, retaining the outstanding redox ability of the CuO/C₃N₄ nanocomposite for the effective generation of active species.¹⁶¹

The photocatalytic efficacy of the CuO/g-C₃N₄ S-scheme nanocomposite obtained *via* hydrothermal growth of CuO over g-C₃N₄ was also tested for degradation of xanthate.¹⁶² Compared with pure g-C₃N₄, the photocatalytic degradation performance of the composite photocatalyst improved by a factor of 5.2. Thurga *et al.*,¹⁶³ tested the H₂ evolution activity of the CuO/g-C₃N₄ system during formaldehyde photoreforming. The authors measured the bandgap energies of CuO and exfoliated g-C₃N₄ to be 1.85 and 2.85 eV, respectively. The CB and VB positions were calculated to be −0.98 and −0.77 eV for g-C₃N₄, and +1.87 eV and +1.08 eV for CuO, respectively. The Mott–Schottky (M–S) analysis revealed n- and p-type semiconducting characteristics of g-C₃N₄ and CuO, respectively. Based on these results, the photocatalytic mechanism and charge transfer process were proposed. Upon contact, electrons will move from exfoliated g-C₃N₄ toward CuO due to Fermi level differences until equilibrium is achieved. Consequently, an IEF at the interface could promote the migration of charge carriers and limit their recombination. Upon light irradiation, the S-scheme mechanism governs the charge transfer such that photogenerated holes and electrons are maintained at the CB and VB of g-C₃N₄ and CuO, triggering H₂ reduction and formaldehyde oxidation, respectively. This charge carrier separation granted the nanocomposite with



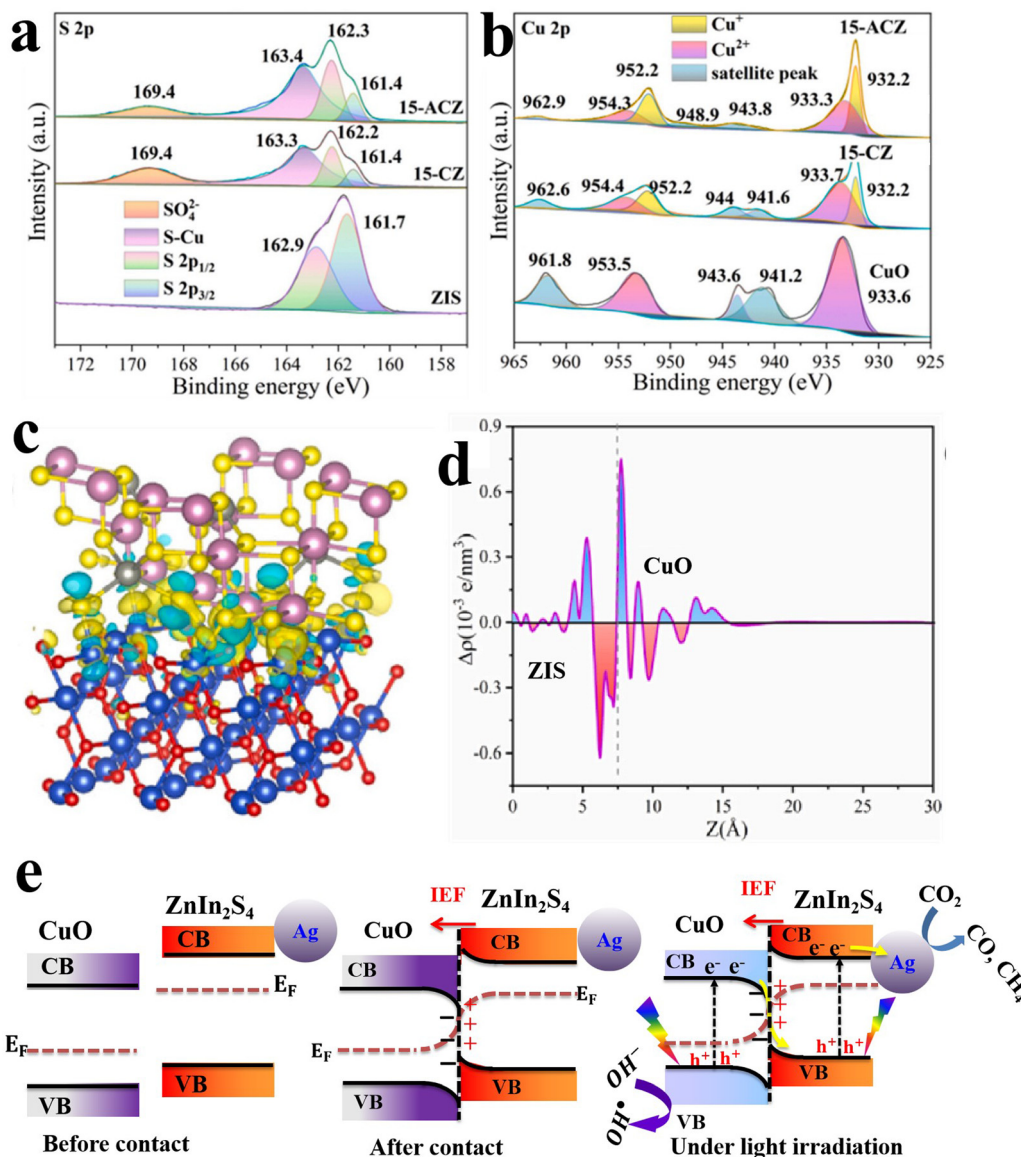


Fig. 23 High-resolution XPS core levels of (a) S 2p and (b) Cu 2p; the simulated charge density difference (c) and planar average charge difference density (d) over the ZIS/CuO composite. Reproduced with permission.¹⁵⁹ Copyright 2023, Elsevier. (e) Charge transfer mechanism and CO₂ reduction over the Ag/CuO@ZnIn₂S₄ S-scheme photocatalytic system.

improved H₂ evolution activity *ca.* 7 and 13 times higher than that of exfoliated g-C₃N₄ and CuO, respectively.

In these studies, the nanocomposite showed good cycling stability, manifesting the robustness of CuO/g-C₃N₄ S-scheme heterojunctions during photocatalytic applications. Other carbon-based materials in combination with CuO to construct S-scheme photocatalytic systems have not yet been reported.

6.1.2.5. Other CuO-based S-scheme heterojunctions. Many innovative S-scheme heterojunctions based on CuO can be constructed by leveraging its adequate band positions. Metal chalcogenides, bismuth oxyhalides, polymers, MOFs, and covalent organic frameworks (COFs) are among the various photocatalytic scaffolds that can be integrated with CuO to form prospective S-scheme heterojunctions. An attempt was made by

Parsaei, Rashid, and coworkers to deliberately construct InP/CuO-C cubic heterostructures derived from an In/Cu bimetallic MOF followed by calcination and phosphitization steps (Fig. 24a).¹⁶⁴ The InP/CuO nanocomposite retained the cubic morphology of pristine In/Cu-MOFs, yet with pronounced porosity (Fig. 24b and c). The photocatalytic activity of the obtained catalyst was investigated for degradation of ciprofloxacin (CIP) antibiotic in a microfluidic photoreactor (Fig. 24a). Different parameters affecting the catalyst performance such as catalyst dose and CIP concentration were studied. The CIP photodegradation efficiency increased from 48.0 to 64.9% as the amount of InP/CuO-C rose from 1.0 to 2.0 mg. However, further increasing the catalyst loading to 3.0 mg resulted in a decline in the photodegradation efficiency to 52.4% (Fig. 24d). In contrast, the photodegradation efficiency gradually decreased with increasing CIP



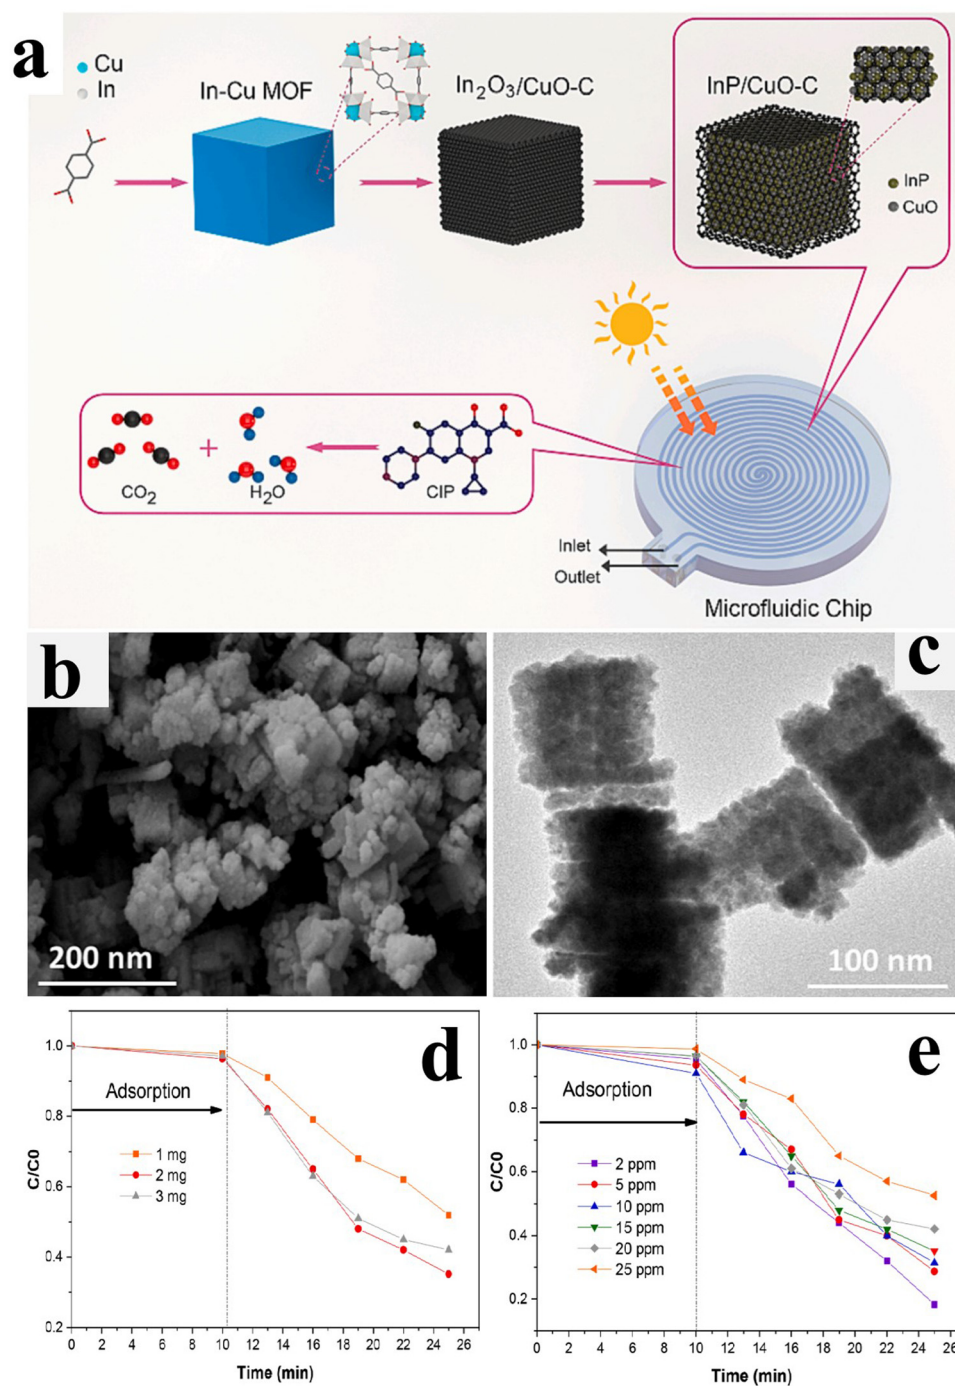


Fig. 24 (a) Schematic illustration of InP/CuO-C fabrication from the In/Cu-MOF precursor and CIP photodegradation in a spiral microfluidic photoreactor; FESEM (b) and TEM (c) images of the InP/CuO-C sample. Photodegradation efficiency of CIP over InP/CuO-C at different InP/CuO-C dosages (d), and different CIP concentrations (e). Reproduced with permission.¹⁶⁴ Copyright 2023, Elsevier.

concentration due to the blocking of the catalyst confined active sites after the adsorption of CIP from the solution thus preventing the adsorption of more CIP molecules (Fig. 24e).

Regarding the charge transfer pathway and reaction mechanism, the work functions of CuO and InP were found to be 5.5 and 4.6 eV, respectively, implying charge transfer from InP into CuO after contact to equilibrate Fermi levels between them and confirming the formation of an IEF. Upon exposure to light,

electrons in the CuO CB will recombine with holes in the InP VB. This scenario lays the foundation for a possible S-scheme charge transfer pathway. Meanwhile, photogenerated charge carriers with stronger redox capacities were retained to trigger the formation of reactive species or used directly to activate CIP degradation.

6.1.3. Cu-based binary oxides. Compared to metal oxides, the electronic properties of binary oxides are significantly



Table 5 S-scheme heterojunction systems of different Cu-based binary oxides with various photocatalytic materials. The S-scheme heterojunctions are arranged in the order OP/RP

S-scheme heterojunction	Application	Efficiency	Ref.
TiO ₂ spindle/CBO	TC degradation	Degradation of 82% in 60 min	190
Fe ₂ O ₃ /CBO	4-NP and RhB degradation	Degradation of 90.6 and 95.8% for 4-NP and RhB after 50 and 40 min, respectively	191
CeO _{2-x} /CBO	Toluene degradation	Degradation of 100% in 120 min	192
WO ₃ /CBO	TC degradation	Degradation of 70% in 120 min	193
Bi ₂ S ₃ /CBO	MB and MO degradation	Degradation of 98.8 and 99.2% for MB and MO after 80 min, respectively	194
BiOBr/CBO	TC degradation	Degradation of 90.3% in 35 min	176
BiOCl/CBO	Diclofenac (DCF) degradation	Degradation of 90% in 60 min	195
Bi ₄ O ₅ I ₂ /CBO	<i>E. coli</i> and <i>S. aureus</i> deactivation	Inactivation of 100% <i>E. coli</i> in 20 min and <i>S. aureus</i> in 40 min	196
(BiO) ₂ CO ₃ /CBO	RhB and MO degradation	Degradation of 97.8 and 98.3% of RhB and MO within 70 min	197
WO ₃ /CBO	CO ₂ reduction	CO and CH ₄ yields of 980.4 and 63.7 μmol m ⁻² , respectively, after 7 h	198
Na-P25/CBO	H ₂ generation	H ₂ yield of 2695.7 μmol g ⁻¹ h ⁻¹	196
MnO ₂ /CFO	MB degradation	Degradation of 92.5% in 240 min	199
ZnIn ₂ S ₄ /CFO	CIP degradation	Degradation of ~100% in 60 min	200
CWO/Bi ₁₂ O ₁₇ Cl ₂	TC degradation	Degradation of 94.7% in 30 min	188

altered after hybridizing O 2p orbitals with additional metallic d-states.¹⁸² Such hybridization results in a bandgap reduction, thereby enhancing visible light absorption and improving carrier mobility. Alternatively, spinel-type compounds, with the general formula of AB₂O₄, comprise octahedral B(III)O₆ units between tetrahedral A(II)O₄ units, characterized by unique physical and chemical aspects. The spatial arrangement of adjacent cations A and B in spinel promotes catalytic activity through lattice electron exchange. Owing to their unique physical, chemical, optical, and electronic properties, spinel materials have attracted significant attention in the heterogeneous photocatalysis realm.^{183–186} CuBi₂O₄ and CuFe₂O₄ are representative candidates of spinel compounds containing Cu²⁺ ions. Apart from spinel structures, Cu can also form binary oxides with other transition metals. Examples are Cu₂V₂O₇,¹⁸⁷ CuWO₄,^{182,188} and CuMnO_x.¹⁸⁹ Cu-doped metal oxides are beyond the scope of this review. In the following sections, Cu-based binary oxides integrated into S-scheme heterojunctions will be discussed in detail. Table 5 summarizes such heterojunctions applied for different photocatalytic applications.

6.1.3.1. CuBi₂O₄. Dibismuth copper oxide (CuBi₂O₄, CBO) is a p-type semiconductor with a narrow bandgap (1.5–1.8 eV), thus exhibiting light absorptivity in the whole visible region. It possesses a sufficiently negative CB to trigger most photocatalytic reduction reactions of current interest. The spinel structure of CBO renders it with exceptional stability thus avoiding photo-corrosion occurring in single Cu or Bi oxides.^{191,192,195,201} Owing to these ample features, CBO has been widely integrated into S-scheme photocatalysts in combination with metal oxides,^{190–193,197,198,201–208} bismuth oxyhalides,^{176,195,196} and metal sulfides.¹⁹⁴ Most of these studies employed the one-step approach to prepare CBO, in which Bi³⁺ and Cu²⁺ are allowed to react with a suitable base (usually NaOH) under hydrothermal conditions. The obtained 1D CBO microrods can be introduced as a substrate during the solvothermal growth of another component. Alternatively, it can be fed into the spraying mixture to be loaded over the target fiber or semiconductor thin film.¹⁹³

Generally, CBO-based S-scheme heterojunction photocatalysts have been used for environmental remediation applications

including organic pollutant degradation, bacteria inactivation, and Cr(vi) reduction. In these systems, CBO functions as a potent RP, where photogenerated electrons with the highest reduction potential reside in its highly negative CB. For example, the degradation efficiency of the Fe₂O₃/CBO S-scheme heterojunction photocatalyst for 4-nitrophenol (4-NP) and RhB reached 90.6% and 95.8% after 50 and 40 min, respectively, of visible light irradiation.¹⁹¹ Interestingly, a mixed solution of 4-NP and RhB pollutants was mostly decomposed after 120 min of natural sunlight irradiation. The ESR and XPS results manifested that an S-scheme charge transfer mechanism was implemented at the interface in such a way that electrons with the highest reduction potential accumulate in the CBO CB to activate O₂ reduction into •O₂⁻. Meanwhile, photogenerated holes at the Fe₂O₃ VB were either used directly for pollutant degradation or to oxidize hydroxide ions into hydroxyl radicals. Photogenerated holes, •O₂⁻ and •OH, were found to be the main reactive species responsible for the degradation of 4-NP and RhB.

Borjigin *et al.*¹⁹² fabricated an oxygen vacancy (OV)-rich CeO₂/CBO S-scheme system for photocatalytic oxidation of gaseous toluene. CeO_{2-x} nanoplates were grown over CBO nanorods using a solvothermal approach. High-resolution TEM images showed the CeO_{2-x} surface with numerous distinct lattice disorders (OV). The existence of OV was also confirmed *via* a distinctive EPR signal at *g* = 2.003 (Fig. 25a). Noteworthy, the OV-signal in the composite sample persists even after five reuses, indicating the excellent stability of OV in the composite material, which contributed to sustaining the activity of the prepared catalyst. To investigate the strong electronic interaction between CBO and CeO_{2-x} in the composite sample, the authors performed DFT simulations.

The results depict the electron density difference at the interface where electron depletion (negative values of Δρ) and enrichment (positive values of Δρ) regions appear at the CBO and CeO_{2-x} sides, respectively, indicating electron transfer from CBO to CeO_{2-x} across the heterojunction interface (Fig. 25b). Such electron transfer after compositing is responsible for the formation of an IEF, thus driving S-scheme electron transfer under light irradiation. Supported by the OV and the S-scheme mechanism, the optimum CBO/CeO_{2-x}



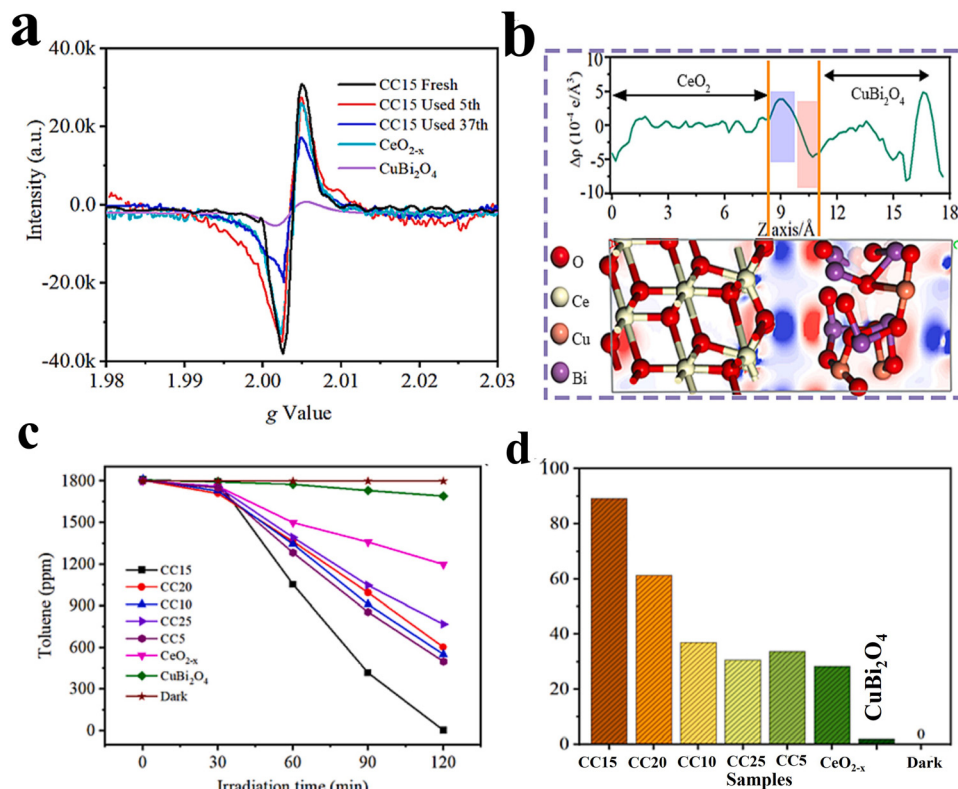


Fig. 25 (a) EPR spectra of pure CeO_{2-x}, CBO, and fresh and used CeO₂/CBO with optimal CBO loading (CC15) sample; (b) the electron density differences transection map and planar-averaged electron density difference, $\Delta\rho$ along the Z-axis for CeO_{2-x}/CBO, where the red and blue regions correspond to the electron depletion and enrichment region, respectively. Toluene degradation (c) and CO₂ yield (d) as a function of irradiation time over the as-prepared catalysts. Reproduced with permission.¹⁹² Copyright 2024, Elsevier.

composite showed upgraded toluene degradation of 100% after 120 min together with TOC removal of $\sim 90\%$ (Fig. 25c and d). Interestingly, the CBO/CeO_{2-x} catalyst retained its excellent degradation activity even after 32 recycling tests.

In another study, the Cu²⁺/Cu⁺ redox cycle was found to effectively sustain the PMS activation of the CBO/BiOBr S-scheme photocatalyst during TC degradation in a Fenton-like process.¹⁷⁶ Compared with bare CBO and BiOBr, the CBO/BiOBr S-scheme photocatalyst degraded 90.3% of TC within 35 min, with the reaction rate increased by 8.4 and 3.3 times, respectively. The S-scheme-induced accumulated electrons at the CBO CB can efficiently sustain the Cu²⁺/Cu⁺ redox cycle, thus maintaining the activity of the CBO/BiOBr nanocomposite. These studies ultimately illustrate the effectiveness of CBO-based S-scheme heterojunctions for environmental remediation. Besides the S-scheme heterojunction enhancing the charge separation and maintaining the highest redox potential during the degradation process, additional contributors can introduce more functionalities and improve the activity and stability of the system. Loading cocatalysts, defect engineering, and incorporating redox pairs are promising strategies to achieve these goals.¹⁹⁴

Apart from pollutant degradation, CBO-based S-scheme photocatalytic systems have also been tested for other energy-related applications such as H₂ evolution²⁰² and CO₂ reduction.^{198,203} For

instance, Shi *et al.*¹⁹⁸ showed that the CO₂ reduction activity is strongly correlated to the heterojunction formation between WO₃ and CBO. Bare WO₃ and CBO exhibited almost no valuable product upon visible light illumination. However, CO and CH₄ were detected as major products after the construction of the WO₃/CBO S-scheme junction, and the product yield increased gradually with CBO content. The optimal yields of CO and CH₄ after 7 h irradiation were 980.4 and 63.7 $\mu\text{mol m}^{-2}$, respectively, attained for WO₃/CBO-4 (4 is the number of spraying cycles for introducing CBO). The authors confirmed the establishment of an S-scheme charge transfer mechanism through different data, such as time-resolved photoluminescence (TRPL), ISIXPS, and catalytic activity measurements under various light conditions.

In these studies, it was argued that the accumulated electrons in the CBO CB, after being separated following an S-scheme trend, are used to accomplish CO₂ reduction or H₂ evolution. Meanwhile, holes in the VB of the OP were consumed for oxidation reactions. In general, CBO is an outstanding RP alternative. Its S-scheme materials exhibited superior activity in various photocatalytic applications with notable stability.

6.1.3.2. CuFe₂O₄. Copper ferrite (CuFe₂O₄, CFO) with a spinel structure and p-type semiconducting nature possesses excellent visible absorption and carrier mobility. These merits render CFO double functionality in S-scheme heterojunctions



as a reducing photocatalyst and Fenton activating agent during pollutant degradation. In particular, the CFO role in environmental remediation includes activating the $\text{Fe}^{3+}/\text{Fe}^{2+}$ and $\text{Cu}^{2+}/\text{Cu}^+$ redox pairs, which can enhance the generation of free radicals and active species responsible for the catalytic activity of the system. In this context, CFO was coupled with MnO_2 and ZnIn_2S_4 to construct S-scheme heterojunctions for MB degradation and a self-Fenton system for CIP mineralization, respectively.^{199,200} The construction of a S-scheme heterojunction between CFO and ZnIn_2S_4 was supported through different means including ISIXPS, ESR, activity measurements, and DFT simulations.²⁰⁰ All methods confirmed charge transfer from CFO to ZnIn_2S_4 after contact. The authors measured the generated H_2O_2 in the system and found that CFO/ ZnIn_2S_4 (1:5) (1:5, representing the weight ratio of CFO to ZnIn_2S_4) afforded the maximum yield of $2545.4 \mu\text{mol g}^{-1} \text{h}^{-1}$, which was 3.9 and 19.3 times higher compared to CFO and ZnIn_2S_4 . The *in situ* generated H_2O_2 was effectively used to produce reactive species efficient for the degradation of numerous organic pollutants, including CIP, sulfamethoxazole, and amoxicillin, with excellent activity and stability. Notably, Fe^{2+} and Cu^+ in CFO/ ZnIn_2S_4 were the main active sites to activate H_2O_2 to generate $\bullet\text{OH}$. The photogenerated electrons accumulated in the CB of CFO, following the S-scheme charge separation pathway, could reduce Fe^{3+} and Cu^{2+} to maintain the cycling of $\text{Fe}^{3+}/\text{Fe}^{2+}$ and $\text{Cu}^{2+}/\text{Cu}^+$ pairs. This sustained the continuous generation of active Fe^{2+} and Cu^+ species for further CIP degradation. This study provides comprehensive insights into the integration and manipulation of CFO-based S-scheme heterojunction photocatalysts. Despite the promising potential of CFO as an RP, its integration into S-scheme systems remains limited.

6.1.3.3. CuWO_4 . Copper tungstate (CuWO_4 , CWO) is a promising n-type semiconductor with a narrow bandgap of ~ 2.2 – 2.4 eV, highly positive VB position and adequate chemical stability.^{182,188} Therefore, CWO is widely employed as an OP. Except for integration with $\text{Bi}_{12}\text{O}_{17}\text{Cl}_2$ to construct an S-scheme system for TC degradation, no research studies have been conducted to explore the potential of CWO in the corresponding S-scheme systems. A CWO/ $\text{Bi}_{12}\text{O}_{17}\text{Cl}_2$ S-scheme heterojunction with rich OV was obtained using a simple precipitation method.¹⁸⁸ CWO NPs were attached to $\text{Bi}_{12}\text{O}_{17}\text{Cl}_2$ NSs with strong interaction between CWO and $\text{Bi}_{12}\text{O}_{17}\text{Cl}_2$ as revealed from HRTEM images and XPS data. Due to the contribution of several factors, including enhanced light absorption, reduced electron–hole recombination, and longer photogenerated electron lifetime, the optimal CWO/ $\text{Bi}_{12}\text{O}_{17}\text{Cl}_2$ exhibited the highest activity. In the S-scheme configuration, the photogenerated electrons and holes were retained in the CB of $\text{Bi}_{12}\text{O}_{17}\text{Cl}_2$ and the VB of CWO, respectively, contributing effectively to the production of reactive species.

6.2. Cu-based chalcogenides

Copper-based chalcogenide materials are chemical compounds composed of Cu (whether solely or encompassing additional

transition metal, main-group metal or semi-metal ions) are bonded to one or more chalcogenide elements (S, Se, or Te). Cu chalcogenides are a versatile class of interesting materials with structural and compositional flexibility, several types of crystal structures, semiconducting nature with often a p-type entity and prominent optical features including small bandgap, high absorption coefficient and highly negative CB position, thus fitting well as the RP in S-scheme heterojunctions.^{209–213} The family includes copper sulfides (Cu_xS , ($1 \leq x \leq 2$)), copper-based binary sulfides (e.g.: CuInS_2 , Cu_2WS_4 , Cu_2MoS_4 , Cu_3SnS_4), and copper selenides (CuSe). This section will provide a detailed overview of copper-based chalcogenide photocatalytic materials, particularly sulfides and selenides, their optical and electronic properties, and possible integration in S-scheme heterojunctions. Table 6 summarizes S-scheme heterojunctions based on Cu-containing chalcogenides for different photocatalytic applications.

6.2.1. Copper sulfides. Copper sulfides (Cu_xS , ($1 \leq x \leq 2$)) are a versatile class of metal chalcogenides with unique p-type semiconducting natures and x-dependent narrow bandgaps varying from about 1.2 eV for Cu_2S ($x = 2$), 1.5 eV for $\text{Cu}_{1.8}\text{S}$ to 2.0 eV for CuS ($x = 1$).²⁴³ Cu_{2-x}S structures with tailored composition and variable concentration of Cu vacancies show extra absorption bands in the near-infrared (NIR) region due to the LSPR effect. Owing to these unique structural, optical, and electronic properties, considerable efforts have been devoted to the synthesis of diverse S-scheme configurations based on Cu_{2-x}S .^{224,244–249} Most studies conducted so far have focused on the integration of Cu_{2-x}S with sulfide-based photocatalytic materials to construct S-scheme heterojunctions such as Bi_2S_3 ,²⁵⁰ ZnIn_2S_4 ,^{215,216} CdZnS ,²¹⁸ MnCdS ,^{219,220} SnIn_4S_8 ,²¹⁷ and Ga_2S_3 .²¹⁴

To ameliorate the performance of pristine CuS during CO_2 photoreduction, improve CO_2 adsorption and activation, and enhance the product selectivity, Ga_2S_3 (GS) was coupled to CuS to build an S-scheme heterojunction using a two-step hydrothermal synthesis.²¹⁴ The 30-GS/ CuS (with 30% wt of GS) S-scheme photocatalyst afforded after 4 hours irradiation of CH_4 yielded $75.2 \mu\text{mol g}^{-1}$, markedly surpassing that of GS ($3.4 \mu\text{mol g}^{-1}$) and CuS ($3.7 \mu\text{mol g}^{-1}$). In addition, the GS/ CuS S-scheme photocatalyst showed no notable decline in activity after five consecutive cycles to check the catalytic stability. Based on bandgap and band energy levels, KPFM measurements, and DFT calculations, the authors were able to assign GS and CuS as the OP and RP, respectively, and propose a plausible charge transfer direction following the S-scheme mechanism. After constructing the S-scheme heterojunction between CuS and GS, the IEF at the interface caused a shift in the d-band center towards the Fermi level, which not only accounts for favorable adsorption and subsequent activation of CO_2 molecules, but also a higher selectivity toward CH_4 . This study sheds light on the underlying mechanism behind the activity and selectivity enhancement caused by a typical S-scheme heterojunction.

On the one hand, hollow morphological structures impart some advantages to photocatalytic materials including large specific surface area, enhanced light absorption due to light reflection within the hollow cavities, reduced mass, shorter charge diffusion lengths, and high density of active sites on



Table 6 S-scheme photocatalytic systems containing different Cu-based photocatalysts (chalcogenides, phosphides, and MOFs) for diverse applications. The configuration of these systems is indicated as OP/RP

S-scheme heterojunction	Application	Efficiency	Ref.
Ga ₂ S ₃ /CuS	CO ₂ reduction	CH ₄ yield of 18.8 μmol g ⁻¹ h ⁻¹	214
CuS/ZnIn ₂ S ₄	H ₂ generation	H ₂ yield of 4653.43 μmol h ⁻¹ g ⁻¹	215
CuS/ZnIn ₂ S ₄	CO ₂ reduction	CH ₄ and CO yields of 4.8 and 55.3 μmol g ⁻¹ h ⁻¹ , respectively	216
CuS/SnIn ₄ S ₈	H ₂ generation	H ₂ yield of 6235.72 μmol g ⁻¹ h ⁻¹	217
CuS/CdZnS	H ₂ generation	H ₂ yield of 5904 μmol g ⁻¹ h ⁻¹	218
CuS/Mn _{0.5} Cd _{0.5} S	H ₂ generation	H ₂ yield of 40.6 mmol h ⁻¹ g ⁻¹	219
CuS/Mn _{0.3} Cd _{0.7} S	H ₂ generation	H ₂ yield of 42.43 mmol g ⁻¹ h ⁻¹	220
CuS/ZnCoS ₂	H ₂ generation	H ₂ yield of 6167 μmol g ⁻¹ within 3 h	221
CuS/Bi ₅ O ₇ I	<i>E. coli</i> disinfection	Complete inactivation in 180 min	222
CuS/Cu-BDC MOF	H ₂ generation	H ₂ yield of 9343 μmol g ⁻¹ h ⁻¹	223
CuS/g-C ₃ N ₄	TC degradation	Degradation of 95% after 40 min	224
WO ₃ /CuInS ₂	TCH degradation	Complete degradation in 6 h	225
SnNb ₂ O ₆ /CuInS ₂	Cr(vi) reduction	Degradation of 97.6% after 90 min	226
UiO-66 MOF/CuInS ₂	N ₂ fixation and O ₂ reduction	NH ₃ and H ₂ O ₂ yields of 398 and 4073 μmol g ⁻¹ h ⁻¹ , respectively	51
Zn _{0.5} Cd _{0.5} S/CuInS ₂	H ₂ generation	H ₂ yield of 7.73 mmol g ⁻¹ h ⁻¹	227
ZnIn ₂ S ₄ /CuInS ₂	TC degradation and Cr(vi) reduction	Degradation of 90.1 and 98.7% for TC (120 min) and Cr(vi) (60 min)	228
g-C ₃ N ₄ /CuInS ₂	O ₂ reduction	H ₂ O ₂ yield of 1247.6 μmol g ⁻¹ h ⁻¹	229
Cu ₂ WS ₄ /CdS	H ₂ generation	H ₂ yield of 6017 μmol g ⁻¹ h ⁻¹	230
MoS ₂ /Cu ₂ WS ₄	BP-1 degradation and Cr(vi) reduction	Degradation of 89.1 and 98.7% for Cr(vi) and BP-1, respectively, in 90 min	231
Cu ₂ MoS ₄ /Cd _{0.9} In _{0.1} Se	H ₂ generation	H ₂ yield of 6358.42 μmol g ⁻¹ h ⁻¹	232
BiOBr/Cu ₃ SnS ₄	CIP degradation	Degradation of 93% after 180 min	233
CuSe/PANI	MB degradation	Degradation of 100% after 45 min	234
TiO ₂ /Cu ₃ P	H ₂ generation	H ₂ yield of 5.83 mmol g ⁻¹ h ⁻¹	235
BiOCl/Cu ₃ P	TC degradation	Degradation of 86% after 6 min	236
ZnWO ₄ /Cu-MOF	TC degradation	Degradation of 98% after 60 min	45
In-MOF@Cu-MOF	Cr(vi) reduction	Reduction of 98% after 60 min	237
Cu-MOF/CuInS ₂	H ₂ generation	H ₂ yield of 1013.35 μmol g ⁻¹ h ⁻¹	238
Cu-MOF/Mn _{0.05} Cd _{0.95} S	H ₂ generation	H ₂ yield of 547.5 μmol after 5 h	239
Cu-MOF/Cd _{0.5} Zn _{0.5} S	H ₂ generation	H ₂ yield of 18986 μmol g ⁻¹ h ⁻¹	240
CeO ₂ /Cu-TCPP MOF	CO ₂ reduction	CO and CH ₄ yield of 57.41 and 3.46 μmol g ⁻¹ h ⁻¹ , respectively	241
Cu-MOF/COF	H ₂ generation	H ₂ yield of 15.3 mmol g ⁻¹ h ⁻¹	242

both sides of the shells.^{215,251} All these merits endowed hollow photocatalysts with special attention in environmental remediation and energy conversion and storage applications.^{252–255}

On the other hand, photothermal catalysis is an innovative approach that combines photochemical and thermocatalytic processes offering promising potential to maximize solar energy utilization. During the process, the required thermal and chemical energy is provided by incident light that impinges the catalyst. When a photothermal catalyst absorbs photons, it converts solar energy into two essential components, hot energetic carriers and localized thermal energy. Both are used to trigger target reactions in a highly efficient and selective manner. In particular, photothermal catalysts can efficiently utilize NIR, which accounts for more than half of the sunlight energy, thus realizing the full-solar-spectrum utilization. Photothermal catalysis may exhibit ample advantages of high conversion efficiencies without additional energy inputs, reducing reaction barriers, and increasing reaction selectivity.^{256–258}

To combine the benefits of photothermal catalysis and hollow morphology, Wang *et al.*,²¹⁵ constructed Cu_{2-x}S hollow nanoboxes using a hard template approach. Then, ZnIn₂S₄ NSs were grown on the outer surface of Cu_{2-x}S hollow nanoboxes using a hydrothermal process (Fig. 26a). The perfect cubic and hollow morphology was observed *via* SEM and TEM imaging (Fig. 26b–g). An IR camera was used to detect the photocatalyst surface temperature change as a function of irradiation time. Starting with a temperature of 15 °C, Cu_{2-x}S@ZnIn₂S₄ had the

highest temperature rising trend within 120 s, reaching *ca.* 52.4 °C (Fig. 26h), owing to the thermal heating by LSPR decay and multiple reflections of light inside the hollow nanoboxes. The photothermal effect results from the strong UV-vis-NIR light absorption of the photothermal catalyst. The obtained core-shell Cu_{2-x}S@ZnIn₂S₄ catalyst exhibited excellent performance for H₂ production with a rate of *ca.* 4653.43 μmol h⁻¹ g⁻¹, which is 137.6 and 13.8 times higher than pure Cu_{2-x}S and ZnIn₂S₄, respectively, and adequate stability.²¹⁵ Both the activity and stability enhancements are rational consequences of the synergistic action of the thermal effect and S-scheme charge transfer mechanism.

When Au NPs are inserted into the interfaces of CuS@ZnIn₂S₄ nanoboxes, the recombination of useless charges under the influence of the S-scheme charge transfer mechanism is promoted through the CuS → Au → ZnIn₂S₄ pathway, thus enabling a more thorough separation of useful ones for CO₂ reduction and H₂O oxidation. Upon LSPR excitation, they can generate hot electrons and holes followed by respective injection into ZnIn₂S₄ and CuS, thus maximizing redox reaction efficiency.²¹⁶ To further optimize the surface reaction kinetics, the authors anchored Fe(OH)_x and Ti₃C₂ MXene inside and outside of Cu_{2-x}S@Au@ZnIn₂S₄ nanoboxes, as oxidation and reduction cocatalysts, respectively. The spatially separated cocatalysts not only maximize the separation of useful photo-generated electron-hole pairs, but also enrich the reactive sites for the selective conversion of CO₂-to-CH₄.

It is worth mentioning that the photothermal effect can induce several positive effects during the water-splitting



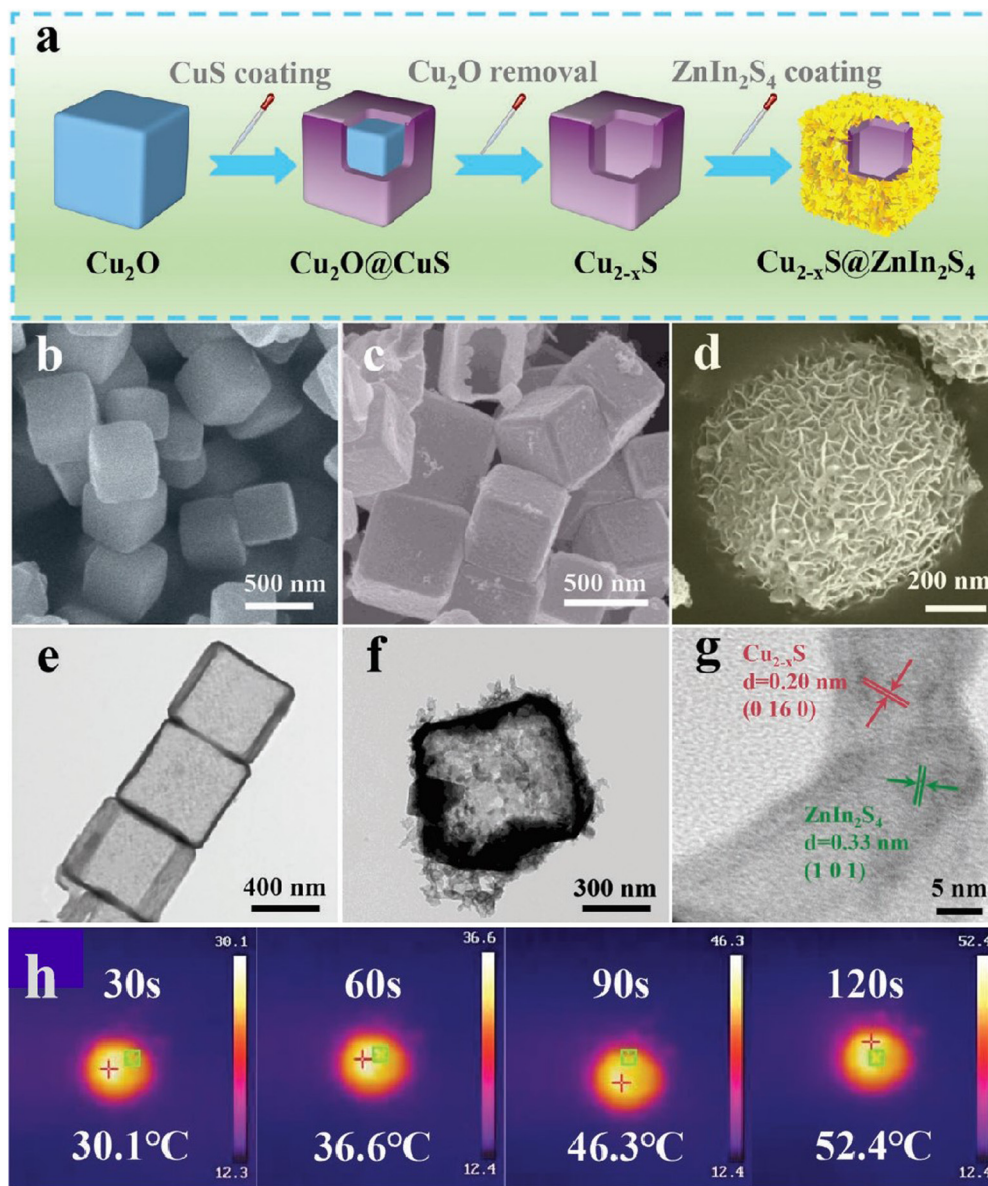


Fig. 26 (a) Scheme illustrating the preparation processes of $\text{Cu}_{2-x}\text{S}@Z\text{nIn}_2\text{S}_4$ core-shell hollow nanoboxes. FESEM images of Cu_2O nanoboxes (b), Cu_{2-x}S hollow nanoboxes (c), and $\text{Cu}_{2-x}\text{S}@Z\text{nIn}_2\text{S}_4$ core-shell hollow nanoboxes (d). TEM images of Cu_{2-x}S (e) and $\text{Cu}_{2-x}\text{S}@Z\text{nIn}_2\text{S}_4$ (f) and (g); (h) the images of the vertical view of $\text{Cu}_{2-x}\text{S}@Z\text{nIn}_2\text{S}_4$ powders under 300 W Xe lamp illumination for different times recorded on an IR thermal camera. Reproduced with permission.²¹⁵ Copyright 2022, Wiley-VCH.

reaction. These effects include: (i) elevated temperature, even to convert liquid water into vapor with a lower adsorption energy barrier; (ii) the raised temperature at the close vicinity of the active site will provide energy to overcome the activation barrier for adsorption and reaction of involved intermediates, and (iii) enhanced separation efficiency of photogenerated carriers by increasing their mobility.²⁵⁹ All these factors are in favor of accelerating the kinetics of the H_2 evolution reaction. Inspired by these attributes, Sun and coworkers²¹⁷ integrated CuS hierarchical spheres with SnIn_4S_8 to construct an S-scheme photothermal catalyst applied for H_2 production *via* a low-temperature wet chemical synthesis. The photocatalytic activity was tested under different light wavelength zones of UV-vis and

UV-vis-NIR, to analyze the NIR-induced thermal contribution to the overall activity. Fig. 27a depicts the average H_2 evolution rate over different catalysts under both conditions. Obviously, the composite samples showed outstanding H_2 evolution activity under UV-vis-NIR irradiation, almost three times higher than that under UV-vis only. This finding ultimately confirms the favorable role of the photothermal effect in promoting the efficiency of H_2 evolution reactions (Fig. 27b). Such a peculiar effect deserves significant research attention in the near future, particularly in the field of environmental remediation.

Apart from sulfide-based photocatalytic materials, CuS is also integrated with metal oxides,^{260–262} bismuth oxyiodide,²²² $\text{g-C}_3\text{N}_4$,²²⁴ and MOFs²²³ to construct S-scheme heterojunctions.



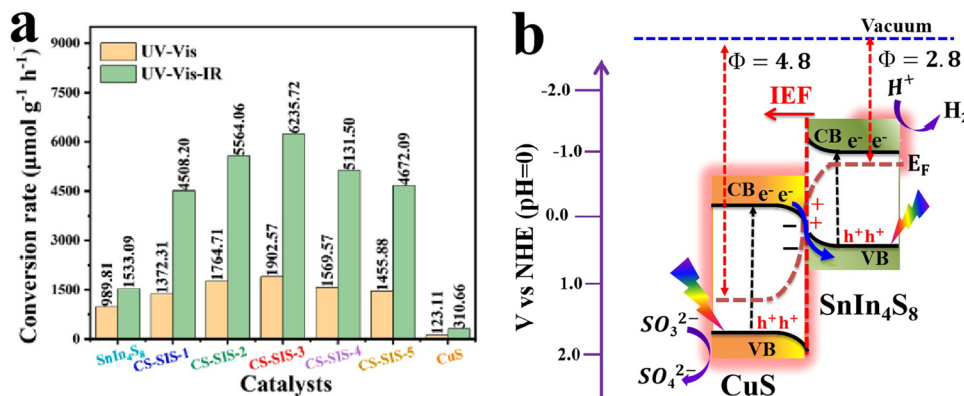


Fig. 27 (a) Average photocatalytic H₂ production over different CuS catalysts under UV-vis and UV-vis-IR illumination. Reproduced with permission.²¹⁷ Copyright 2024, Elsevier. (b) Illustration of the charge transfer mechanism over the CuS/SnIn₄S₈ S-scheme heterojunction. The red glow shows the photothermal effect due to LSPR on CuS.

Due to nonstoichiometric Cu_{2-x}S being a degenerately self-doped p-type semiconductor, it displays a composition-dependent LSPR covering a very broad range from NIR to mid-IR.²⁶³ Consequently, its light-harvesting ability can be tailored to cover the entire range of the solar spectrum and develop a full-spectrum-based photocatalyst. In this context, multiple S-scheme photocatalysts based on Cu_{2-x}S have been reported as absorbing the entire UV-vis-NIR light to enhance their photocatalytic activity.

For example, roxbyite (Cu_{1.8}S, CS) with nanoplate (np) and snowflake (sf) morphologies were prepared under solvothermal conditions by varying the sulfur source and subsequently used as the substrate and copper source for the *in situ* growth of Cu-BDC-NH₂ MOF to construct CS/Cu-MOF (CSM) S-scheme heterojunctions.²²³ The *in situ* growth synthesis allows for strong bonding and intimate interfacial contact between CS and the Cu MOF that promotes efficient intergranular charge migration separation. The obtained nanocomposite exhibited strong light absorption over the entire solar spectrum benefiting from the unique LSPR of CuS and the distinct absorption features of the Cu-MOF. Therefore, the optimal CSM (sf) hybrid displayed an improved photocatalytic activity with H₂ evolution rate of 9343 μmol g⁻¹ h⁻¹ and O₂ reduction rate of 2339 μmol g⁻¹ h⁻¹, 14–20 times greater than the pure components. The full spectrum-response property of CuS-based S-scheme systems was also reported for heterojunctions with g-C₃N₄,²²⁴ g-C₃N₄/Bi₂S₃²⁵⁰ and VO₂.²⁶² Since CuS was used as the OP in most of these studies, the stability is again an important concern with possible activity decline over long-term usage due to surface oxidation and/or photo-corrosion by accumulated photogenerated holes unless a suitable oxidation cocatalyst is attached to boost the on-time photogenerated hole consumption.

6.2.2. Cu-based binary sulfides. Compared to monometallic sulfides, bimetallic sulfides provide greater versatility for atomic and electronic structure tuning.^{233,264} Copper-based binary sulfides (*e.g.*: CuInS₂, Cu₂WS₄, Cu₂MoS₄, Cu₃SnS₄, among others) are typical candidates with visible light harvesting ability and adequate electronic properties. Their integration in S-scheme heterojunctions has been extensively reported.

Table 6 summarizes various S-scheme heterojunctions based on Cu-based chalcogenides, phosphides, and MOFs.

6.2.2.1. CuInS₂. CuInS₂ (CIS) has a narrow direct band gap of ~1.5 eV, ultrahigh absorption coefficient (1 × 10⁵ cm⁻¹), and negative CB position (~-0.5 to -1.4 V vs. NHE),^{265,266} making it an appropriate choice as a RP in S-scheme photocatalysts. Therefore, CIS has been extensively studied in S-scheme configurations with TiO₂,²⁶⁷ WO₃,²²⁵ SnNb₂O₆,²²⁶ Bi₂MoO₆,²⁶⁸ g-C₃N₄,^{229,269,270} Zr-MOF,⁵¹ Zn_{0.5}Cd_{0.5}S,²²⁷ and ZnIn₂S₄.²²⁸ Composites of CIS are prepared either by the *in situ* growth approach over the target support or by mixing CIS with the other component in an appropriate solvent followed by evaporating such solvent. For instance, when copper sulfate pentahydrate, indium chloride tetrahydrate, and thiourea (representing CIS precursors) were mixed with a certain amount of WO₃ nanosheets and the mixture was transferred to a Teflon-lined autoclave and kept at 433 K for 24 h to allow *in situ* growth of CIS NSS, a 2D/2D interfacial contact heterojunction was constructed.²²⁵ WO₃ exhibited a distinct band edge at ~490 nm, while CIS showed its strong light absorption feature throughout the entire wavelength range. Accordingly, the light-harvesting ability of CIS/WO₃ nanocomposites was drastically improved in the visible region compared to that of pure WO₃ (Fig. 28a). The catalytic activity of the prepared samples was investigated for degradation of tetracycline hydrochloride (TCH) in a Fenton-like process. CIS/WO₃ with an optimum amount of WO₃ degraded TCH completely in 6 h (Fig. 28b) and the photocatalyst retains its initial activity even after five successive recycling tests (Fig. 28c). Experimental measurements show that the VB and CB potentials of the n-type WO₃ are 2.69 and 0.1 V, while those of the CIS are 1.03 and -0.46 V, respectively, all against RHE. Fig. 28d presents the band structure of the CIS/WO₃ nanocomposite. Based on these findings, it is reasonable to conclude that the observed activity cannot be explained in terms of the type-II heterojunction charge transfer mechanism. Instead, the S-scheme configuration rationalizes that the photogenerated electrons and holes responsible for TCH degradation reside on the CIS CB and WO₃ VB, respectively.²²⁵

Importantly, the removal of organic pollutants through oxidative degradation can be combined simultaneously with



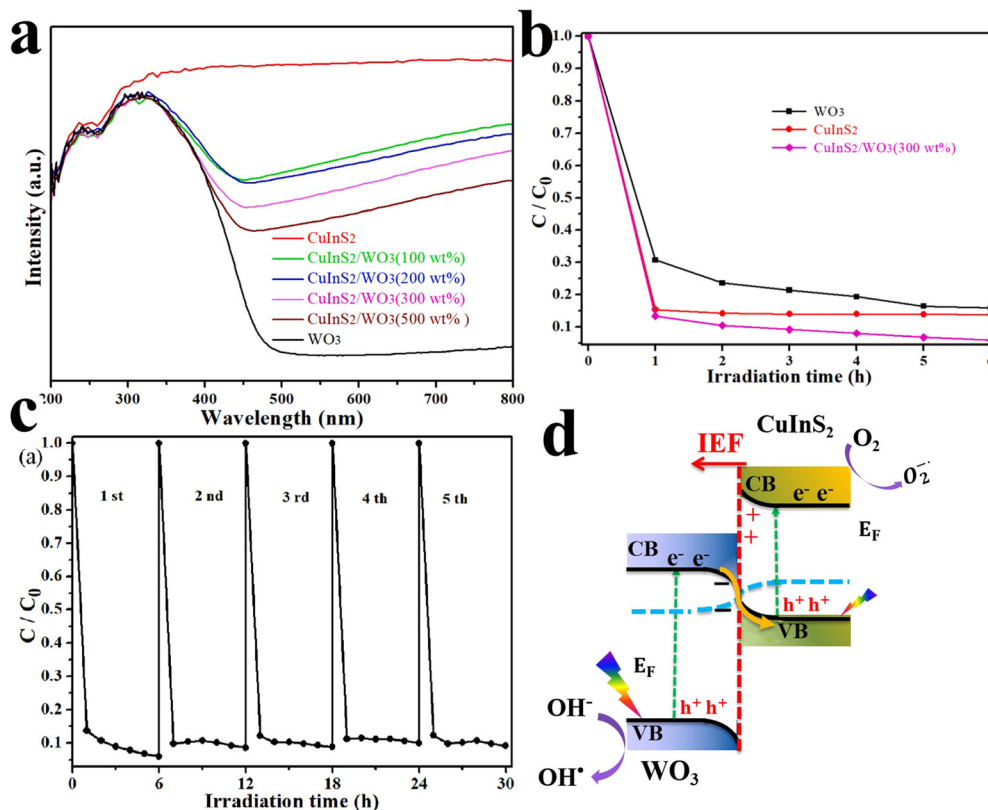


Fig. 28 (a) UV-vis DRS profiles of CIS, WO₃, and CIS/WO₃ hybrid heterostructures with different WO₃ contents. (b) Photocatalytic activity of WO₃, CIS, and the CIS/WO₃ (300 wt%, representing the content of WO₃ in the composite) hybrid heterostructure during the photo-Fenton degradation of TCH. (c) Recycling test of the CIS/WO₃ composite sample. Reproduced with permission.²²⁵ Copyright 2023, Elsevier. (d) Schematic representation of the band structure and charge transfer migration over the CIS/WO₃ S-scheme heterojunction.

suitable reduction reactions to make full use of photogenerated electron-hole pairs in both processes of the overall redox reaction. For example, the oxidation of organic pollutants can be accomplished in line with the reduction of Cr(vi) to the less toxic Cr(III). Under these circumstances, the organic pollutant serves as a sacrificial agent to scavenge photogenerated holes, while separated electrons are used to trigger Cr(vi) reduction. Liu and coworkers found that the Cr(vi) reduction efficiency over SnNb₂O₆/CuInS₂ S-scheme heterojunctions was greatly enhanced after introducing TCH as a target organic pollutant and hole scavenger.²²⁶ The apparent rate constants for Cr(vi) reduction and TCH oxidation in a mixed pollutant system were increased by 3.74 and 1.58 times, respectively, compared to the mono-pollutant system. This finding indicates that organic pollutants can act as electron donors to consume photoinduced holes and enable more photoexcited electrons to be consumed for photoreduction reactions. The ability of an organic material to support the bi-directional promotion effect is inversely related to its ionization potential (IP), such that pollutants with lower IP indeed have higher electron-donating abilities. Thus, these electron donors possess a higher potential to promote the reduction of the electron acceptor pollutant through the operation of the S-scheme charge migration mechanism.

Alternately, it has been proven that defect engineering is a highly effective approach for enriching surface active sites,

enhancing light absorption, and boosting the separation of photogenerated charge carriers.^{271–273} For example, sulfur vacancy (SV), which is a conventional defect unveiled by metal sulfides, was found to play a role as an active center for promoting reactant adsorption and activation.^{51,274} When the CIS photocatalyst was allowed to grow over UiO-66-NH₂ (UiO-66) using a low-temperature deposition technique, SV was generated in the crystal lattice of CIS. Fig. 29a illustrates the preparation protocol for the UiO-66/CIS composite. The existence of SV was assured by ESR measurements, where a sharp signal at $g = 2.004$ was attributed to SV. The emergence of SV after the growth of CIS over UiO-66 MOF not only accounts for the improved light absorption and quenched fluorescence, but also for enriching active sites available for adsorption and activation of O₂ and N₂ gaseous molecules during their respective reduction. Therefore, the optimal UiO-66/CIS20 photocatalyst exhibited notable reduction performances for N₂ and O₂ with yields of 398 and 4073 $\mu\text{mol g}^{-1} \text{h}^{-1}$, respectively, 6–20 times higher than those of pure components (Fig. 29b and c). The outstanding activity and excellent stability were assigned to the S-scheme charge transfer action. When UiO-66 is combined with CIS, the staggered band alignment allows for charge migration according to the S-scheme mechanism.

Under light illumination, photogenerated electrons and holes with the lower redox potentials become recombined.



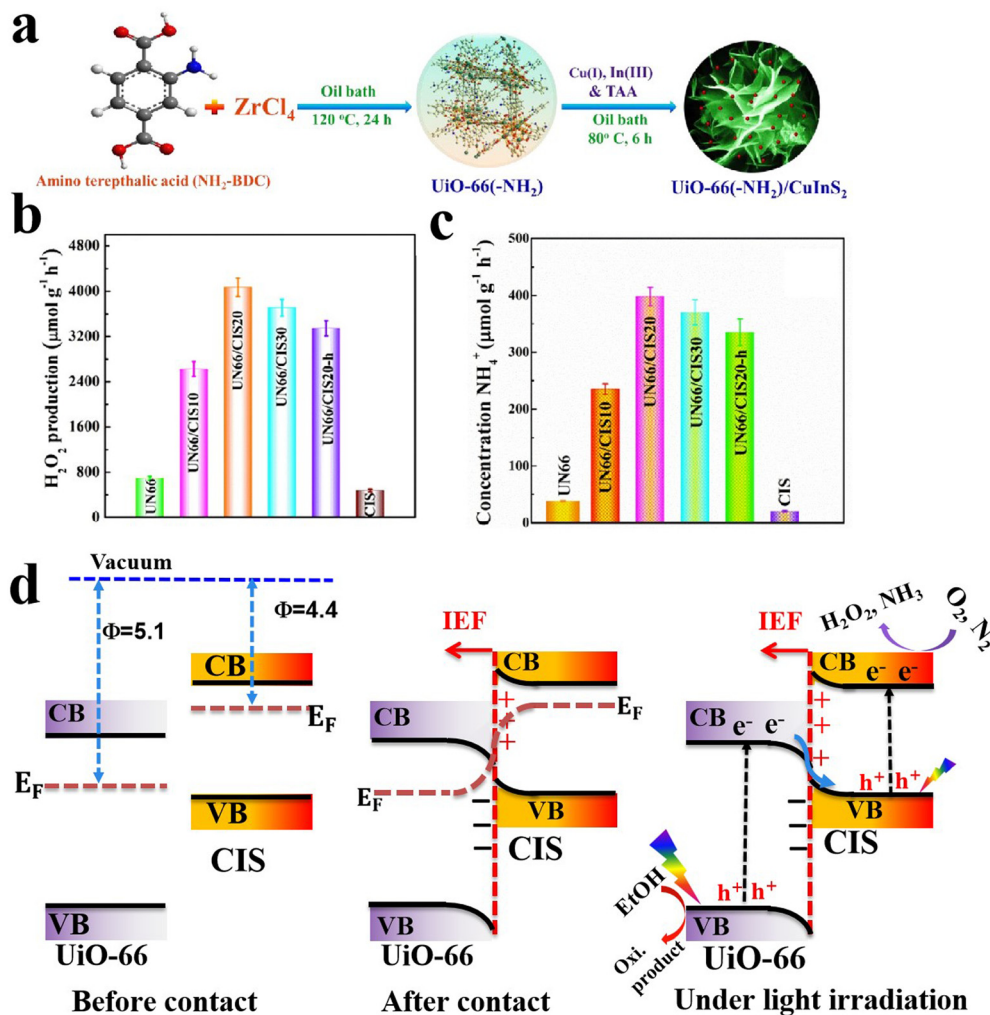


Fig. 29 (a) Fabrication of UiO-66/CIS S-scheme heterojunctions. Photocatalytic performances of the prepared catalysts for (b) H₂O₂ production and (c) N₂ fixation. Reproduced with permission.⁵¹ Copyright 2023, American Chemical Society. (d) Schematic representation of the band edge potentials of pure CIS and UiO-66 components and plausible S-scheme charge transfer mechanisms in the UiO-66/CIS heterostructures.

Meanwhile, most reducing electrons are maintained at the CIS CB to participate in O₂ or N₂ reduction reactions (Fig. 29d).⁵¹ The functional role of SV was also reported for the Zn_{0.5}Cd_{0.5}S/CIS S-scheme heterojunction during H₂ evolution reaction.²²⁷ These studies shed light on the synergistic effect of atomic vacancy and S-scheme heterojunction systems for photocatalytic applications.

Although defect engineering as a tool to increase the efficiency of conventional photocatalysts (including enhancing light absorption ability, modifying electronic features and improving catalyst reactivity) has been widely appreciated,^{251,275–277} its specific contributions to S-scheme heterojunctions have been almost overlooked. These include, but are not limited to, enhanced charge separation, longer carrier lifetime, and higher efficiency of surface catalytic reactions. With adequate control over defect type, level, and position, it is possible to tune the charge carrier dynamics and reaction efficiency and even change the charge separation mechanism from type-II to the more favorable S-scheme mechanism. For instance, Xu *et al.*,²⁷² developed a tunable defect-level-assisted

strategy to tailor the OV content in WO_{3-x}/In₂S₃ S-scheme heterojunctions. The concentration of OVs, along with the induced defect level depth, plays a crucial role in determining the strength of IEF established at the heterojunction interface and thus in the charge separation efficiency. An elevated OV concentration or deep defect levels can lead to excessive charge trapping, which diminishes the charge carrier mobility and worsens photocatalytic activity.²⁷⁸ They found that an intermediate defect level induced by a controlled quantity of OVs in the WO_{3-x}/In₂S₃ heterojunctions serves as an electron reservoir for effectively prolonging charge carrier lifetimes, promoting the formation of a strong IEF for effective separation of photogenerated electron-hole pairs and hence improving the photocatalytic efficiency. Owing to this distinct role, combined with the extended carrier lifetime, the WO_{3-x}/In₂S₃ S-scheme heterojunction afforded excellent CO₂ photoreduction with nearly 100% CO selectivity. Furthermore, the introduced impurities can adjust the electronic features of the bare semiconductor, enriching the charge carrier concentration in such a way that a switch in the charge transfer mechanism from type-II heterojunction to



S-scheme pathway occurs.⁶⁸ In general, defect engineering has promising potential for designing effective S-scheme heterojunctions and controlling their features such as redox abilities, charge carrier lifetime, and hence reaction efficiency.

6.2.2.2. Cu_2WS_4 . With a narrow bandgap of approximately 2.1 eV, suitable band positions, and co-exposed (101) and (002) crystal facets, Cu_2WS_4 is a fascinating visible light-responsive photocatalyst. The controlled tuning of the (101) and (002) crystal planes allows for the construction of a homojunction at the interface of these planes, which enhances charge separation under the S-scheme mechanism when integrated with a suitable counterpart. In this way, it is possible to prepare a homojunction/heterojunction system based on Cu_2WS_4 . Due to its distinct set of optical and electronic properties, Cu_2WS_4 with a predominant (101) facet exhibits strong oxidation ability, while Cu_2WS_4 with a predominant (002) facet shows a strong reduction

ability. The precise control over crystal facets enables the design of Cu_2WS_4 with desirable electronic and optical properties for targeted applications.^{230,231,279} For example, Cu_2WS_4 with a predominant (101) facet was synthesized and used to anchor CdS NPs through a hydrothermal approach.²³⁰ The morphology of Cu_2WS_4 resembles nanoplates with exposed (101) facets (Fig. 30a–c), while CdS NPs are aggregated on the surface of the Cu_2WS_4 nanoplates (Fig. 30b and c). The light absorption of Cu_2WS_4 is mainly concentrated in the visible region, with an additional absorption tail extending into the NIR. However, the absorption of the composite sample (CSS10) is further enhanced after CdS is combined with Cu_2WS_4 (Fig. 30d). According to Tauc plot analysis, the bandgaps of Cu_2WS_4 and CdS were determined to be approximately 2.13 eV and 2.15 eV, respectively. The composite $\text{Cu}_2\text{WS}_4/\text{CdS}$ S-scheme heterojunction photocatalyst exhibited H_2 evolution activity that was about 21.3 times higher than that of pure CdS and 33.4 times higher than that of Cu_2WS_4 . This improved activity was

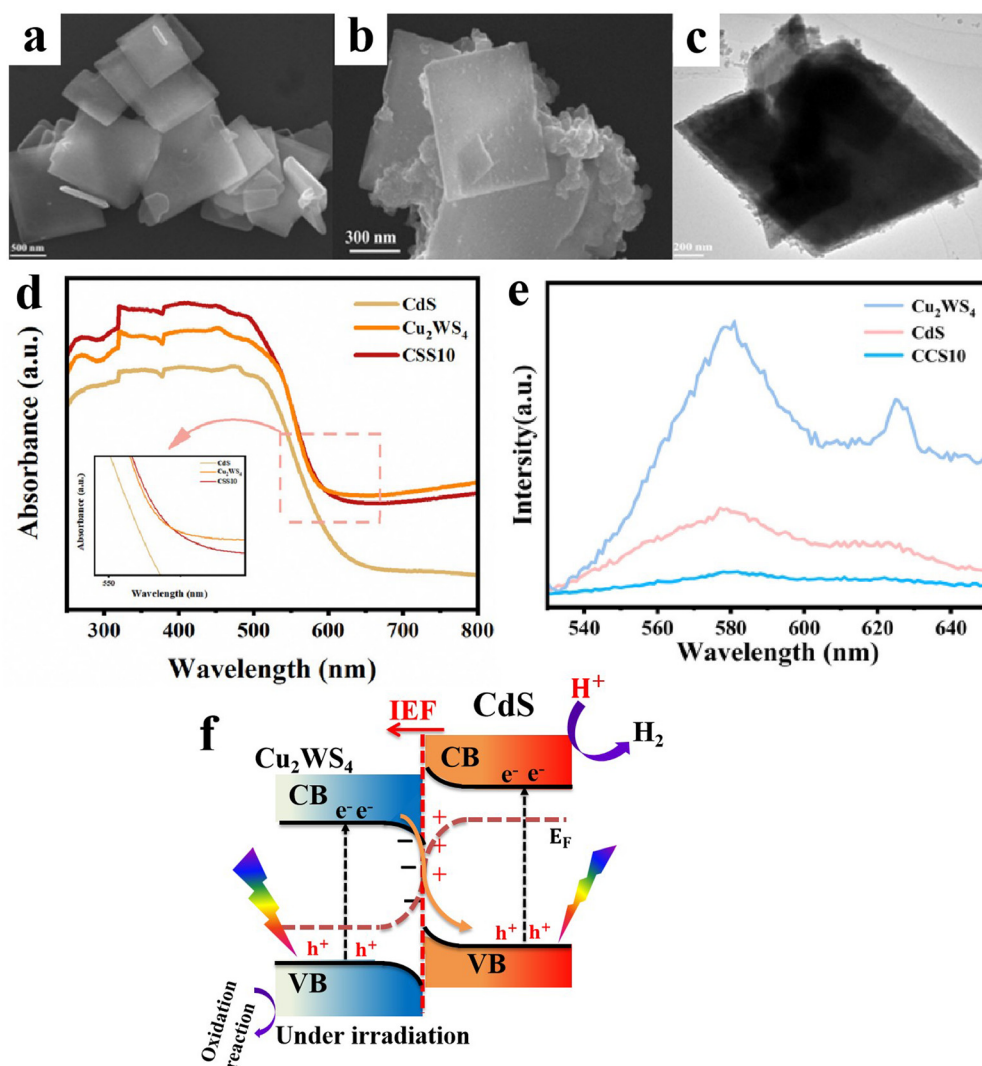


Fig. 30 SEM images of (a) Cu_2WS_4 and (b) $\text{Cu}_2\text{WS}_4/\text{CdS}$ -10 (CSS10); (c) TEM image of CSS10; DRS (d) and PL curves (e) of the prepared photocatalysts. Reproduced with permission.²³⁰ Copyright 2023, Royal Society of Chemistry. (f) Band structure and proposed charge migration pathway over the $\text{Cu}_2\text{WS}_4/\text{CdS}$ S-scheme heterojunction.



attributed to the enhanced light absorption and suppressed charge recombination after integrating CdS and Cu₂WS₄ into an S-scheme configuration (Fig. 30d and e). By considering the CB position of each component (as revealed by M-S measurements), and the work function values based on DFT simulations and band positions, the authors used ISIXPS analysis to support their proposed S-scheme charge migration pathway as depicted in Fig. 30f. When CdS is irradiated, the photogenerated holes are consumed by recombination with electrons from Cu₂WS₄. Meanwhile, photo-generated holes on Cu₂WS₄ after light excitation selectively migrate to the (101) crystal facet, which has a higher oxidation potential. Therefore, separated electrons in the CB of CdS are used to drive the HER, while separated holes in the VB of Cu₂WS₄ are involved in the oxidation reaction.²³⁰ Overall, crystal facet engineering can maximize the separation and migration of photogenerated electron-hole pairs, thus promoting the S-scheme charge transfer mechanism and enhancing photocatalytic activity.

In another study, the ohmic contact established at the plasmonic Au/MoS₂ interface further enhances the charge separation across the MoS₂/Cu₂WS₄ heterojunction.²³¹ Therefore, the Cu₂WS₄/MoS₂-Au plasmonic heterojunction follows the S-scheme charge transfer mechanism, enabling photoexcited electrons and holes to achieve the highest reduction and oxidation potentials for efficient Cr(vi) reduction and benzophenone-1 pollutant degradation.

Currently, the integration of Cu₂WS₄ in S-scheme photocatalytic systems is limited. In addition, detailed information about Cu₂WS₄ stability during cycling tests still requires careful attention.

6.2.2.3. Other Cu-based binary sulfides. Other Cu-based binary sulfides, including Cu₂MoS₄ and Cu₃SnS₄, have also been reported to form S-scheme heterojunctions.^{233,280} Both compounds can be derived from Cu₂O by distinct approaches in the presence of suitable sulfide and Mo- or Sn-precursors. Cu₃SnS₄ with a highly negative CB at ~ -1.0 V (*vs.* NHE, pH = 0), and a bandgap of *ca.* 1.7 eV can be considered a typical RP. Meanwhile, Cu₂MoS₄, with a bandgap of around 1.9 eV and a CB at approximately -0.55 V (*vs.* NHE), can function either as an RP or an OP depending on the other component in the S-scheme system.

6.2.3. CuSe. Recently, metal selenides, with bandgaps ranging from approximately 1.6 to 2.8 eV, have gained increased attention in photocatalysis and photoelectrochemistry due to their vast solar energy absorption, high CB energy value, and fast charge carrier mobility. Among them, CuSe, a p-type semiconductor, exhibits tailored functional, optical, and electrical properties, a strong absorption cross-section, and a strong LSPR in the NIR, making it a promising candidate for photo- and photothermal catalytic applications. Despite these appealing merits, the integration of CuSe in S-scheme heterojunction photocatalysts remains limited.²⁸¹

Saray and his team constructed S-scheme CuSe/Ag-PANI heterojunctions using a simple and cost-effective co-precipitation.²³⁴ Multiple phases of Cu_xSe_y (CuSe and Cu₃Se₂) were observed in XRD and HRTEM imaging, suggesting possible formation of dual S-scheme heterojunctions. Namely, a homojunction between

different phases of CuSe (since each phase possesses distinct bandgaps and energy edge positions) and a heterojunction between PANI and CuSe. Ag NPs act as an LSPR metal NP, thus strengthening the light absorption extent and as a mediator to boost the migration of photogenerated electrons. Owing to the unique dual S-scheme configuration and the supportive role of plasmonic Ag NPs, the Cu_xSe_y/Ag-PANI nanocomposite degraded MB dye completely in just 45 min, compared to 75 min for Cu_xSe_y/PANI without Ag NPs. The high negative position of CuSe CB, strong light absorption within the vis-NIR region, and its tailorable structural, optical, and electronic properties greatly support its integration as an effective RP in S-scheme configurations for photo- and photothermal catalytic applications.

6.3. Cu-phosphide

Transition metal phosphides with high conductivity, based on earth abundant elements, and high catalytic activity serve as potential catalytic and/or cocatalytic components in energy-related applications.²⁸² Copper phosphide (Cu₃P), which exhibits unique properties such as a narrow bandgap (1.3–1.5 eV), p-type semiconducting behavior and plasmonic response, has recently received increasing interest as a cocatalyst or photocatalyst in heterojunctions.^{283–286} Due to its excellent electron-accepting ability, Cu₃P can be strategically integrated into S-scheme heterojunction configurations to effectively increase the charge transfer and prolong the photoinduced excited electron lifetime for desirable photocatalytic performance.²⁸⁵

When combined with TiO₂ through a microwave hydrothermal approach, the hydrogen production rate of the Cu₃P/TiO₂ S-scheme heterojunction with optimum Cu₃P loading reached 5.83 mmol g⁻¹ h⁻¹, which was 7.3 and 83.3 times higher than that of pure TiO₂ and Cu₃P, respectively (Fig. 31a). This S-scheme heterojunction photocatalyst also displayed notable stability over 8 runs (a total of 40 h) of recycling (Fig. 31b). ISIXPS and DFT calculations were used to verify the S-scheme mechanism. Upon light irradiation, ISIXPS showed that the BE of O 1s becomes positively shifted (indicating that O donates electrons), while that of P 2p decreased significantly (corresponding to an electron gain, Fig. 31c and d). Following XPS data, the average charge density calculations based on DFT revealed that electron depletion and accumulation regions are generated, respectively, over Cu₃P and TiO₂ components (Fig. 31e). These findings firmly support the operation of an S-scheme charge transfer mechanism over the Cu₃P/TiO₂ heterojunction. Initially, electrons are supposed to move from Cu₃P to TiO₂ after constructing the heterojunction. Then, photogenerated electrons at the TiO₂ CB will be transferred to recombine with holes at the Cu₃P VB. The Gibbs free energy (ΔG_{H^+}) calculations indicated that Cu centers are the most favorable sites for H⁺ adsorption (with moderately negative adsorption energy value) (Fig. 31f). Therefore, photogenerated electrons at the Cu₃P CB are located properly to accomplish H⁺ reduction to H₂ at Cu sites.²³⁵

It is noteworthy that the strong atomic interaction between S-scheme heterojunction components at the interface could create interatomic charge transfer channels that facilitate interfacial



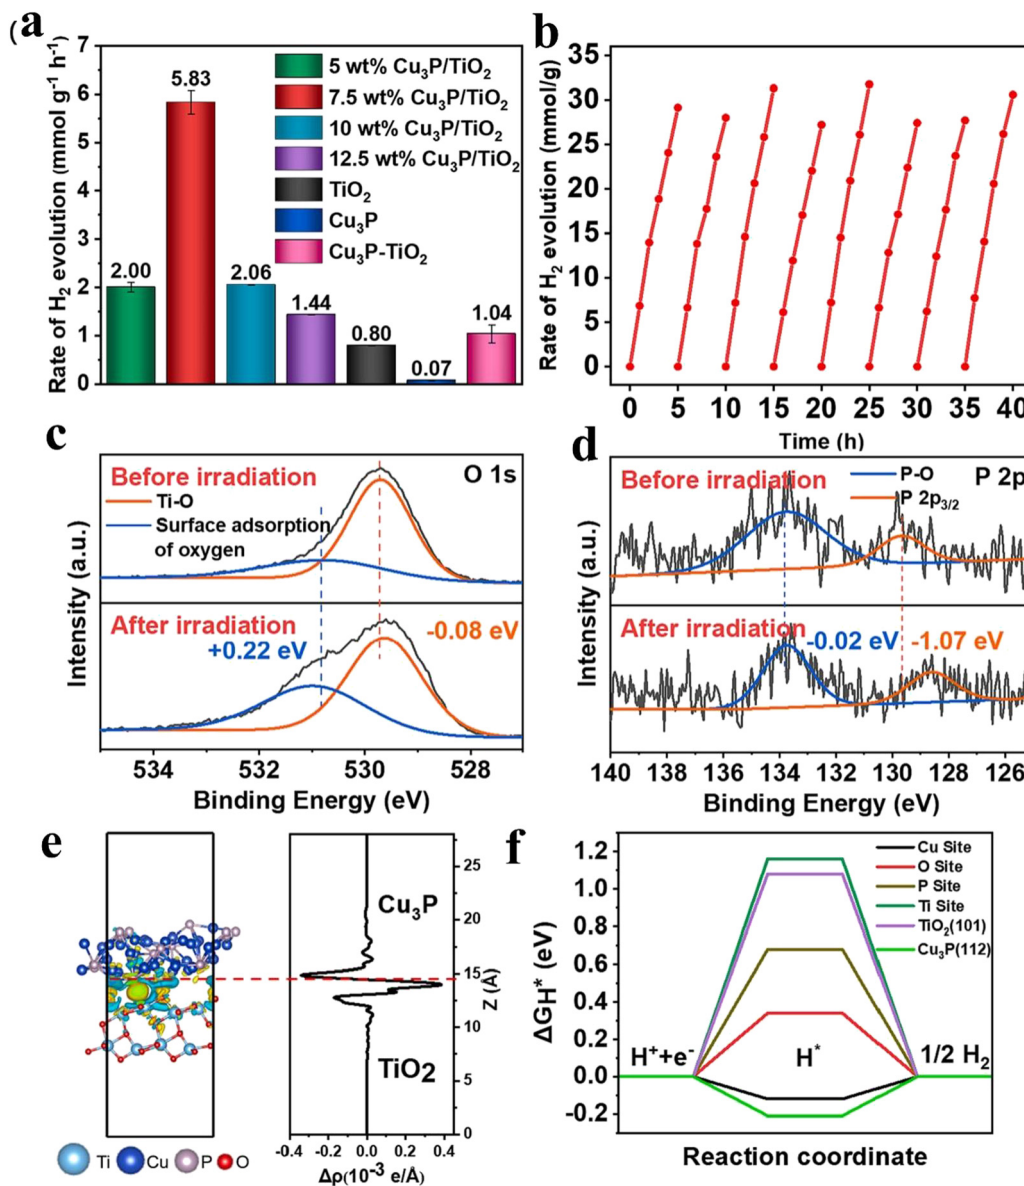


Fig. 31 (a) Photocatalytic hydrogen production rates of the prepared TiO₂, Cu₃P and Cu₃P/TiO₂ with different Cu₃P loadings; (b) stability test (8 cycles in 40 h) for hydrogen production over 7.5 wt% Cu₃P/TiO₂ as a photocatalyst exhibiting the best activity; high-resolution XPS spectra of (c) O 1s and (d) P 2p in Cu₃P/TiO₂ before and after 1 h illumination; (e) planar average charge density difference between TiO₂ and Cu₃P (yellow and green colors indicate electron aggregation and depletion regions, respectively); (f) H adsorption Gibbs free energy calculation over different active sites. Reproduced with permission.²³⁵ Copyright 2023, Elsevier.

charge transfer for efficient photogenerated charge carrier separation. For instance, the strong interatomic interaction between oxygen vacancies (OV) in BiOBr and Cu₃P not only promotes H₂O adsorption at Bi sites, thereby increasing hydrogen production efficiency, but also aids in the migration of photogenerated charge carriers at the interface.²⁸⁶ The newly formed interatomic bonding can fulfill the conditions for better adsorption and activation of reactant molecules.

In another study, Cu₃P quantum dots (QDs) of 3–8 nm in size were grafted onto BiOCl NSs to form a 0D/2D heterostructure and tested for TC degradation. The activity measurements showed improved degradation performance of the composite compared to pristine BiOCl. Characterization data confirmed

that after the heterojunction formation: (i) photoluminescence (PL) was significantly quenched due to suppressed charge recombination; (ii) enhanced photocurrent was observed due to efficient charge separation; and (iii) pronounced ESR signals for the superoxide radical $\cdot\text{O}_2^-$ indicated electron accumulation in the Cu₃P CB. All these results infer the potential of Cu₃P as a viable alternative for efficient S-scheme heterojunction construction. With a sufficiently negative CB position, Cu₃P is well-suited for integration as an RP in S-scheme heterojunctions for better and more stable performances.

Alternatively, phosphosulfides (PS) have received great attention in the catalysis community owing to their structure, which can offer more active sites with better stability than their



phosphide or sulfide counterparts.^{287,288} In this vein, copper phosphosulfide ($\text{Cu}_3\text{P|S}$) has emerged as a potent photocatalyst for H_2 evolution and CO_2 reduction.^{289,290} When 0D $\text{Cu}_3\text{P|S}$ was anchored on 2D $g\text{-C}_3\text{N}_4$ NSs to form a S-scheme heterojunction, interfacial P–N chemical bonds were formed, functioning as electron transfer channels for efficient separation and migration of photogenerated charge carriers. Additionally, the unique PS structure provided abundant active sites for improved CO_2 reduction activity. As a result, an enhanced CO generation rate of $137 \mu\text{mol g}^{-1} \text{h}^{-1}$ was attained, which is 8 and 2.3 times higher than that of pristine $g\text{-C}_3\text{N}_4$ and $\text{Cu}_3\text{P}/g\text{-C}_3\text{N}_4$, respectively.²⁸⁹ Although Cu_3P and $\text{Cu}_3\text{P|S}$ are emerging Cu-based photocatalysts, reports on their integration into S-scheme heterojunctions are still scarce. Therefore, future studies are encouraged to further explore their potential in photocatalytic applications. Interestingly, the SPR response of these materials can be exploited for NIR photocatalysis or photothermal catalysis.

6.4. Cu-MOF

As previously discussed in Section 5.1.1.6, MOFs are porous crystalline materials with a wide range of chemical compositions and they exhibit tunable optical and electronic features, thereby promoting their wide application in photocatalysis. Other photocatalytic scaffolds can be confined within the 3D porous structure of MOFs, allowing for the establishment of strong interfacial contact for accessible charge transfer, and enhancing photocatalytic activity. Following this scenario, Cao *et al.*,²³⁹ anchored $\text{Mn}_{0.05}\text{Cd}_{0.95}\text{S}$ NPs over Cu-BTC MOF regular octahedrons for H_2 evolution applications. Benefiting from the high surface area of Cu-MOFs with a high density of active sites and the S-scheme charge transfer mechanism at the interface, the H_2 evolution activity under LED irradiation was doubled compared to that of pristine $\text{Mn}_{0.05}\text{Cd}_{0.95}\text{S}$. When the composition was changed to $\text{Zn}_{0.5}\text{Cd}_{0.5}\text{S}$, the H_2 evolution performance drastically increased to $18986 \mu\text{mol g}^{-1} \text{h}^{-1}$ for the $\text{Zn}_{0.5}\text{Cd}_{0.5}\text{S}/\text{Cu-MOF}$ octahedron composite, tested under a 300 W Xe lamp.²⁴⁰ Although light intensity is a key factor for the observed photocatalytic activity, normalizing photocatalytic performance using metrics such as the apparent quantum efficiency (AQE) could allow for a more reasonable comparison of results and provide a clearer outlook on current achievements and prospects.

Cu-BTC has been integrated with other inorganic semiconductors such as ZnWO_4 and CuInS_2 to construct S-scheme heterojunctions with improved activity and stability.^{45,238} In these systems, the Cu-BTC MOF exhibited an n-type semiconducting behavior with a large bandgap of ~ 2.8 eV, CB located at ~ -0.55 V (vs. NHE), and a highly positive VB position. Thereby, it functioned as an OP.

Porphyrim is a typical photosensitizer with high visible light absorption and a long-lived excited state.^{291,292} Porphyrim-based MOFs combine the benefits of both porphyrim and MOF, particularly supporting superior electron mobility due to the localization of electrons over an extended π -conjugated system composed of macrocycles. An ultrathin 2D Cu-*meso*-tetrakis(4-carboxyphenyl)-porphyrim (TCPP) MOF is a prime example of porphyrim-based MOFs, showing promising potential for CO_2 reduction due to its

abundant active sites, which favor the adsorption and activation of CO_2 molecules. When combined with oxygen vacancy-rich CeO_2 (LA- CeO_2) prepared following a mild solvothermal synthesis, a unique 0D/2D S-scheme heterojunction structure was constructed (Fig. 32a–e).²⁴¹ The morphology of Cu-TCPP MOF is ultrathin NSs (Fig. 32b), while monodispersed CeO_2 NPs with an average diameter of 22 nm were deposited on them (Fig. 32c and d). Compared with the light absorption of CeO_2 , which is mainly concentrated in the UV region, $\text{CeO}_2@$ Cu-TCPP nanocomposites exhibited excellent light-harvesting ability across the entire UV-vis-NIR region due to various allowed electronic transitions localized on the TCPP moieties. Owing to the strong absorption in the NIR, the $\text{CeO}_2@$ Cu-TCPP nanocomposites displayed a prominent photothermal response as revealed by thermal images taken after light irradiation. $\text{CeO}_2@$ Cu-TCPP with optimum CeO_2 loading showed remarkable photocatalytic CO_2 reduction activity, with CO and CH_4 yields of 229.6 and $13.85 \mu\text{mol g}^{-1}$ after 4 h, which were orders of magnitude higher than those of pristine CeO_2 and Cu-TCPP.

The enhanced activity and stability of $\text{CeO}_2@$ Cu-TCPP were attributed to several factors including (i) a higher content of OVs and hydrophilic –OH groups, which endowed the sample with sufficient active sites for favorable adsorption and activation of CO_2 molecules and accessible mass/charge transfer; (ii) the S-scheme heterojunction established at the n–n type heterojunction that allows electron diffusion from Cu-TCPP to CeO_2 after contact and until equilibrium (Fig. 32f and g) and maintains the most valuable photogenerated electrons and holes with higher redox potential to participate efficiently in the targeted reactions. The photothermal effect also contributed positively to the overall charge separation process (Fig. 32h).

As the study pointed out the potential of the Cu-TCPP MOF as a promising 2D photocatalytic component for constructing S-scheme systems, it also highlighted the cumulative function of surface modification, defect engineering, and heterojunction construction toward improving the performance and stability of a photocatalytic system. Table 6 summarizes most S-scheme systems incorporating Cu-MOF as a photocatalytic component.

In this regard, it is important to emphasize the unique features of the 2D materials such as large surface area and thin layered structure. Such peculiar morphology is pivotal for shortening the required diffusion length of charge carriers to react, improved reagent mass transfer and full exposure of the active sites for target photocatalytic reactions. Additionally, the layered morphology favors intimate interfacial contact, thus providing accessible channels for photoinduced charge carrier transfer through the interface and hence better reaction efficiency derived from more efficient charge separation.^{30,293,294} Different combinations based on 2D photocatalytic materials can be designed to fulfill the S-scheme heterojunction perquisites including 0D/2D, 1D/2D and 2D/2D heterojunctions. Excellent reviews summarizing recent progress on 2D materials and their integration in S-scheme heterojunction systems can be found in the literature.^{7,30}

Apart from the 0D/2D configurations discussed in the previous section, the 2D/2D heterojunctions possess ample merits



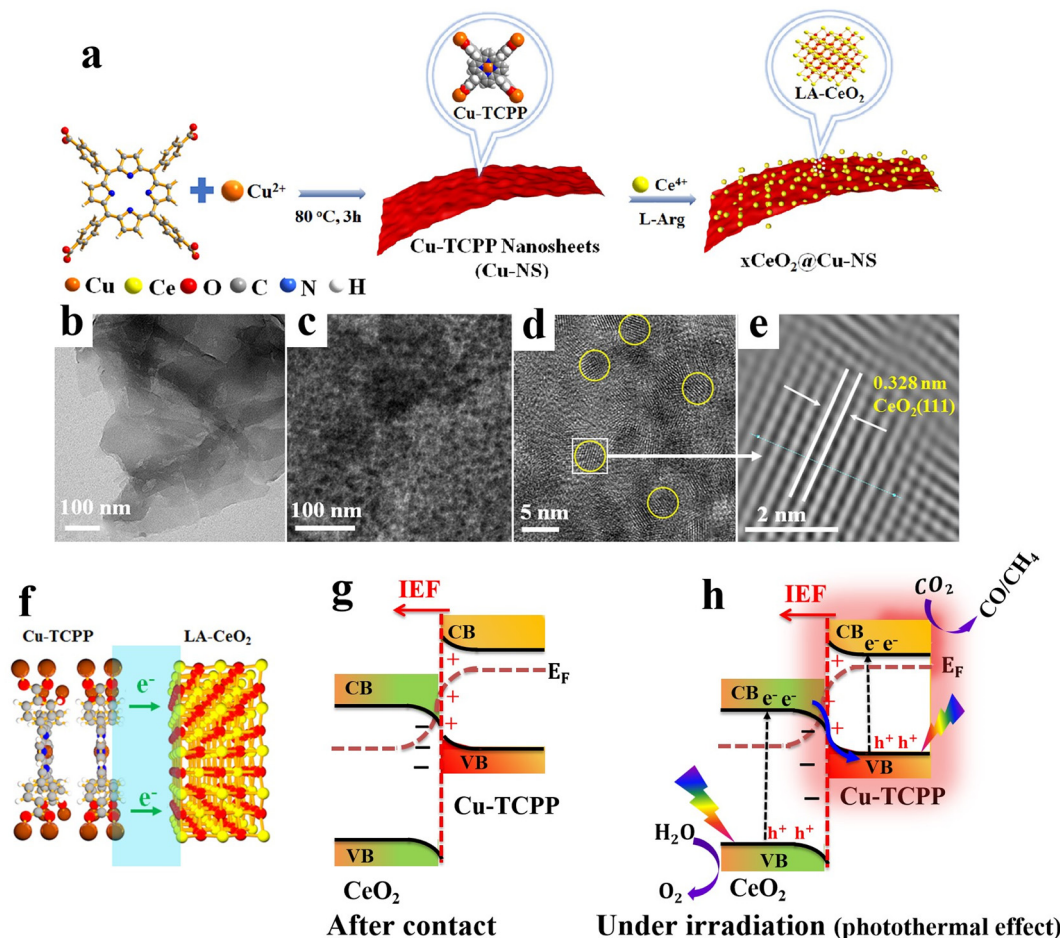


Fig. 32 (a) Schematic of the preparation procedure of the Cu-TCPP MOF and CeO₂/Cu-CTPP S-scheme heterojunction. TEM of Cu-TCPP 2D NSs (b) and single CeO₂ NP (c); HRTEM (d) and FFT image (e) of CeO₂@Cu-TCPP; (f) Electron flow direction within the 0.25CeO₂@Cu-TCPP S-scheme heterojunction photocatalyst; reproduced with permission.²⁴¹ Copyright 2023, American Chemical Society. Schematic illustration of the charge transfer mechanism of the CeO₂@Cu-TCPP S-scheme heterojunction after contact (g) and under light (h).

such as (i) the “face-to-face” contact, enabling an extended interface with better interfacial matching for enhanced charge migration, and (ii) strong electronic coupling between layers, optimizing the electronic structure of the constituent 2D materials for improved catalytic activity.^{242,295–297} Various 2D scaffolds, including g-C₃N₄, graphdiyne, phosphorene, MXenes, 2D MOFs, 2D COFs, and transition metal dichalcogenides, are readily available and confer interest for a versatile family of functional heterojunction materials. Among them, COFs represent a class of porous covalent polymers with high specific surface area, adequate crystallinity, tunable composition, broad light absorption ability, and excellent electron mobility over the extended π -conjugated framework. Under these features, COFs are well-suited candidates for photocatalysis.^{298–301} Recently, Hu *et al.*,²⁴² took advantage of 2D/2D MOF/COF structures to construct a fascinating photocatalytic system for H₂ evolution. Besides the S-scheme charge transfer mechanism, the long-range ordered crystalline structure of both components with a 2D/2D interface contributed markedly to guided charge transfer. The extremely high specific surface area of the integrated materials provided abundant active sites for H⁺ adsorption and

reduction. All these factors contributed to the commendable photocatalytic activity and stability of the Cu-MOF/COF heterostructure.

Although these results are promising, the integration of Cu-MOFs in S-scheme heterojunctions for photocatalytic applications is still limited. COF/MOF-based S-scheme heterojunction photocatalysts are expected to attract considerable interest in future research due to the vast chemical space available for these hybrid composites that allow the design and fine tuning of their optoelectronic properties.

7. Conclusions and perspectives

The construction of S-scheme heterojunctions offers a compelling approach not only for the effective separation of photo-generated charge carriers but also for preserving charges with the highest redox potential at distinct locations. This approach alleviates the challenge of charge recombination and strongly enhances reaction kinetics. In this context, Cu-based photocatalytic materials, including a wide range of compounds such



as oxides, binary oxides, chalcogenides, phosphides, and MOFs, form a versatile family of efficient components for S-scheme heterojunction construction. In this review, we summarized recent progress in the development of S-scheme heterojunctions involving Cu-based photocatalytic materials.

With their narrow bandgaps implying absorption of a wide range of visible light radiation, suitable band positions implying that they can promote useful reduction and some oxidation reactions, and unique structural, optical, and electronic properties, these materials offer multiple opportunities for optimizing the activity, selectivity, and stability of photocatalytic systems for various target applications. The charge separation efficiency, and consequently the activity, can be further enhanced by modifying these materials with cocatalytic moieties such as metallic clusters, carbonaceous materials, and conductive 2D substrates. Newly emerging 2D materials, including MXenes, GDY, and phosphorene, exhibit fascinating electrical conductivity and surface activity, making them excellent candidates for integration into S-scheme systems.

Moreover, constructing strongly interconnected components, even with interfacial covalent bonds and hybridized electronic states can facilitate the appearance of charge transfer channels at the interface, enabling efficient charge carrier migration. In this regard, *in situ* generation methods have proven effective in forming covalent bonds between the components of S-scheme heterojunctions. For example, the formation of Cu–S covalent bonds upon integrating CuO with ZnIn₂S₄ has been found to open accessible pathways for enhanced charge separation and restructure of the electronic arrangement of reacting molecules.

Cu-based photocatalytic materials exhibit a wide range of electronic properties, enabling them to act as either RP or OP depending on their band positions and stability under reaction conditions. Some Cu-chalcogenides and Cu-MOFs exhibit dual functionality as both the RP and OP due to their appropriate band positions. The stability of S-scheme heterojunctions is further enhanced by the spatial separation of electron–hole pairs. For instance, Cu₂O is unstable when used as an OP due to oxidation by accumulated photogenerated holes. Therefore, Cu₂O is better suited for integration as an RP in S-scheme systems to ensure sustainable performance. In this regard, it has been proposed in some cases that the Cu²⁺/Cu⁺ redox pair plays a crucial role in the adsorption and activation of reactant molecules, particularly in pollutant degradation. The partial reduction of Cu²⁺ to Cu⁺ by photogenerated electrons sustains the catalytic cycle in Fenton-like processes, maintaining system activity without the need for external reducing agents.

A variety of photophysical and theoretical approaches have been adopted to study the charge transfer mechanisms within S-scheme heterojunctions. Techniques such as ISIXPS and DFT calculations are widely used to confirm the S-scheme charge transfer mechanism, while fs-TAS is a powerful tool for measuring the lifetime of charge carriers. The extension of charge carrier lifetime or the appearance of new charge transfer processes with distinct lifetimes following heterojunction formation can indicate efficient charge transfer. Advanced characterization techniques

with sufficient temporal and spatial resolution need to be further developed to identify active sites and optimize the activity and stability of these photocatalytic systems.

This review has provided an overview of the current progress in the field, with the aim of guiding future research toward the development of novel, high-performance Cu-based S-scheme photocatalysts and a deeper understanding of their underlying photocatalytic mechanisms. However, there remains significant potential to explore the broader integration of these materials into S-scheme heterojunctions trying to overcome the current bottlenecks in the areas related to efficiency and stability. In particular, Cu₃P and Cu-binary sulfides are promising candidates with unique properties, yet their integration into S-scheme photocatalytic systems has been scarcely studied.

The S-scheme heterojunction photocatalytic system is a rapidly emerging field in the realm of catalysis and is expected to continue to gain prominence. Interest in Cu-based S-scheme heterojunctions is anticipated to grow in the near future, as researchers work to develop photocatalytic systems based on earth-abundant elements. These advancements could bring the commercial production of solar fuels and chemicals closer to reality, helping to meet global energy and environmental demands.

Data availability

No primary research results, software or code have been included and no new data were generated or analysed as part of this review.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors acknowledge the financial support from the National Key Research and Development Program of China (2022YFB3803600); the National Natural Science Foundation of China (W2433135, 22361142704, 22238009, 22261142666 and U23A20102); the Natural Science Foundation of Hubei Province, China (2022CFA001 and 2023AFA088); the Spanish Ministry of Science and Innovation (CEX2021-01230-S and PDI2021-0126071-OB-CO21 funded by MCIN/AEI/10.13039/501100011033) and Generalitat Valenciana (Prometeo 2021/038 and Adv Mater programme Graphica MFA/2022/023 with funding from European Union NextGenerationEU PRTR-C17.I1); this work was also supported by the Fundamental Research Funds for the Central Universities, China University of Geosciences (Wuhan) (no. CUG22061).

References


- 1 B. Wang, G. M. Biesold, M. Zhang and Z. Lin, *Chem. Soc. Rev.*, 2021, **50**, 6914–6949.



- 2 H. Mai, D. Chen, Y. Tachibana, H. Suzuki, R. Abe and R. A. Caruso, *Chem. Soc. Rev.*, 2021, **50**, 13692–13729.
- 3 P. Kumar, G. Singh, X. Guan, J. Lee, R. Bahadur, K. Ramadass, P. Kumar, Md. G. Kibria, D. Vidyasagar, J. Yi and A. Vinu, *Chem. Soc. Rev.*, 2023, **52**, 7602–7664.
- 4 Y. Shi, Z. Zhao, D. Yang, J. Tan, X. Xin, Y. Liu and Z. Jiang, *Chem. Soc. Rev.*, 2023, **52**, 6938–6956.
- 5 X. Tao, Y. Zhao, S. Wang, C. Li and R. Li, *Chem. Soc. Rev.*, 2022, **51**, 3561–3608.
- 6 Z. Wang, Y. Hu, S. Zhang and Y. Sun, *Chem. Soc. Rev.*, 2022, **51**, 6704–6737.
- 7 B. Zhu, J. Sun, Y. Zhao, L. Zhang and J. Yu, *Adv. Mater.*, 2024, **36**, 2310600.
- 8 M. J. Molaei, *J. Am. Ceram. Soc.*, 2024, **107**, 5695–5719.
- 9 K. Sharma, V. Hasija, M. Malhotra, P. K. Verma, A. A. Parwaz Khan, S. Thakur, Q. Van Le, H. H. Phan Quang, V.-H. Nguyen, P. Singh and P. Raizada, *Int. J. Hydrogen Energy*, 2024, **52**, 804–818.
- 10 S. Wageh, A. A. Al-Ghamdi, R. Jafer, X. Li and P. Zhang, *Chin. J. Catal.*, 2021, **42**, 667–669.
- 11 Q. Xu, L. Zhang, B. Cheng, J. Fan and J. Yu, *Chem*, 2020, **6**, 1543–1559.
- 12 J. Low, J. Yu, M. Jaroniec, S. Wageh and A. A. Al-Ghamdi, *Adv. Mater.*, 2017, **29**, 1601694.
- 13 L. Wang, B. Zhu, J. Zhang, J. B. Ghasemi, M. Mousavi and J. Yu, *Matter*, 2022, **5**, 4187–4211.
- 14 L. Wang, J. Sun, B. Cheng, R. He and J. Yu, *J. Phys. Chem. Lett.*, 2023, **14**, 4803–4814.
- 15 A. J. Bard, *J. Photochem.*, 1979, **10**, 59–75.
- 16 L. Wang, C. Bie and J. Yu, *Trends Chem.*, 2022, **4**, 973–983.
- 17 J. Low, C. Jiang, B. Cheng, S. Wageh, A. A. Al-Ghamdi and J. Yu, *Small Methods*, 2017, **1**, 1700080.
- 18 H. Tada, T. Mitsui, T. Kiyonaga, T. Akita and K. Tanaka, *Nat. Mater.*, 2006, **5**, 782–786.
- 19 Q. Xu, L. Zhang, J. Yu, S. Wageh, A. A. Al-Ghamdi and M. Jaroniec, *Mater. Today*, 2018, **21**, 1042–1063.
- 20 J. Yu, S. Wang, J. Low and W. Xiao, *Phys. Chem. Chem. Phys.*, 2013, **15**, 16883–16890.
- 21 J. Fu, Q. Xu, J. Low, C. Jiang and J. Yu, *Appl. Catal., B*, 2019, **243**, 556–565.
- 22 F. Li, G. Zhu, J. Jiang, L. Yang, F. Deng, Arramel and X. Li, *J. Mater. Sci. Technol.*, 2024, **177**, 142–180.
- 23 X. Wang, M. Sayed, O. Ruzimuradov, J. Zhang, Y. Fan, X. Li, X. Bai and J. Low, *Appl. Mater. Today*, 2022, **29**, 101609.
- 24 Q. Xu, S. Wageh, A. A. Al-Ghamdi and X. Li, *J. Mater. Sci. Technol.*, 2022, **124**, 171–173.
- 25 C. Bie, B. Zhu, L. Wang, H. Yu, C. Jiang, T. Chen and J. Yu, *Angew. Chem., Int. Ed.*, 2022, **61**, e202212045.
- 26 X. Wu, G. Chen, J. Wang, J. Li and G. Wang, *Acta Phys.-Chim. Sin.*, 2023, **39**, 2212016.
- 27 S. Rej, M. Bisetto, A. Naldoni and P. Fornasiero, *J. Mater. Chem. A*, 2021, **9**, 5915.
- 28 L. Zhang, J. Zhang, H. Yu and J. Yu, *Adv. Mater.*, 2022, **34**, 2107668.
- 29 B. Zhu, C. Jiang, J. Xu, Z. Zhang, J. Fu and J. Yu, *Mater. Today*, 2025, **82**, 251–273.
- 30 W. Wang, B. Cheng, G. Luo, J. Yu and S. Cao, *Mater. Today*, 2024, **81**, 137–158.
- 31 M. Sayed, B. Zhu, P. Kuang, X. Liu, B. Cheng, A. A. Al-Ghamdi, S. Wageh, L. Zhang and J. Yu, *Adv. Sustainable Syst.*, 2022, **6**, 2100264.
- 32 M. Sabir, M. Sayed, Z. Zeng, B. Cheng, W. Wang, C. Wang, J. Xu and S. Cao, *Appl. Surf. Sci.*, 2025, **693**, 162752.
- 33 A. Zindrou, L. Belles and Y. Deligiannakis, *Solar*, 2023, **3**, 87–112.
- 34 S. Gorsse, M. Gouné, W.-C. Lin and L. Girard, *Sci. Data*, 2023, **10**, 504.
- 35 M. B. Gawande, A. Goswami, F.-X. Felpin, T. Asefa, X. Huang, R. Silva, X. Zou, R. Zboril and R. S. Varma, *Chem. Rev.*, 2016, **116**, 3722–3811.
- 36 R. Zhang, Y. Chen, M. Ding and J. Zhao, *Nano Res.*, 2022, **15**, 2810–2833.
- 37 Y. Du, Y.-T. Tang, X. Ma, J. Li and Q. Guo, *Cryst. Growth Des.*, 2024, **24**, 2592–2618.
- 38 H. Xie, J. Wang, K. Ithisuphalap, G. Wu and Q. Li, *J. Energy Chem.*, 2017, **26**, 1039–1049.
- 39 J. Xia, X. Liu, H. Zhou, L. Pu, J. Zhang, X. Li, F. Li, L. Long, S. Li and Y. He, *Catal. Sci. Technol.*, 2021, **11**, 7905–7913.
- 40 D. Derelli, F. Caddeo, K. Frank, K. Kröttsch, P. Ewerhardt, M. Krüger, S. Medicus, L. Klemeyer, M. Skiba, C. Ruhmlieb, O. Gutowski, A.-C. Dippel, W. J. Parak, B. Nickel and D. Koziej, *Angew. Chem., Int. Ed.*, 2023, **62**, e202307948.
- 41 M. Balık, V. Bulut and I. Y. Erdogan, *Int. J. Hydrogen Energy*, 2019, **44**, 18744–18755.
- 42 K. Jagadish, A. Godha, B. Pandit, Y. Jadhav, A. Dutta, J. Satapathy, H. Bhatt, B. Singh, S. K. Makineni, S. Pal and S. R. Rondiya, *Small*, 2024, **20**, 2405859.
- 43 A. Rahman, J. R. Jennings and M. M. Khan, *Mater. Sci. Semicond. Process.*, 2024, **169**, 107930.
- 44 Y.-Q. Liu, F.-X. Wang, Y. Xiao, H.-D. Peng, H.-J. Zhong, Z.-H. Liu and G.-B. Pan, *Sci. Rep.*, 2014, **4**, 5998.
- 45 J. S. Jeyaprakash, M. Rajamani, C. L. Bianchi, M. Ashokkumar and B. Neppolian, *Ultrason. Sonochem.*, 2023, **100**, 106624.
- 46 M. Haddad, A. Belhadi, L. Boudjellal and M. Trari, *Int. J. Hydrogen Energy*, 2021, **46**, 37556–37563.
- 47 F. Nekouei, S. Nekouei, M. Pouzesh and Y. Liu, *Chem. Eng. J.*, 2020, **385**, 123710.
- 48 T. Xiang, F. Xin, C. Zhao, S. Lou, W. Qu, Y. Wang, Y. Song, S. Zhang and X. Yin, *J. Colloid Interface Sci.*, 2018, **518**, 34–40.
- 49 H. Wu, X. Y. Kong, X. Wen, S.-P. Chai, E. C. Lovell, J. Tang and Y. H. Ng, *Angew. Chem., Int. Ed.*, 2021, **60**, 8455–8459.
- 50 M. Sayed, L. Zhang and J. Yu, *Chem. Eng. J.*, 2020, **397**, 125390.
- 51 R. Bariki, S. K. Pradhan, S. Panda, S. K. Nayak, A. R. Pati and B. G. Mishra, *Langmuir*, 2023, **39**, 7707–7722.
- 52 K. Meng, J. Zhang, B. Cheng, X. Ren, Z. Xia, F. Xu, L. Zhang and J. Yu, *Adv. Mater.*, 2024, **36**, 2406460.
- 53 D. Gholami, S. Shahbazi, S. Mosleh, A. Ghoorchian, S. Hajati, K. Dashtian and G. Yasin, *Chem. Eng. J.*, 2023, **461**, 141950.
- 54 H. Hamad, M. M. Elsenety, W. Sadik, A.-G. El-Demerdash, A. Nashed, A. Mostafa and S. Elyamny, *Sci. Rep.*, 2022, **12**, 2217.



- 55 Q.-Y. Tang, W.-F. Chen, Y.-R. Lv, S.-Y. Yang and Y.-H. Xu, *Sep. Purif. Technol.*, 2020, **236**, 116243.
- 56 R. He, D. Xu and M. Sayed, *J. Materiomics*, 2025, **11**, 100989.
- 57 J. Zhang, B. Zhu, L. Zhang and J. Yu, *Chem. Commun.*, 2023, **59**, 688–699.
- 58 W. Melitz, J. Shen, A. C. Kummel and S. Lee, *Surf. Sci. Rep.*, 2011, **66**, 1–27.
- 59 C. Cheng, B. He, J. Fan, B. Cheng, S. Cao and J. Yu, *Adv. Mater.*, 2021, **33**, 2100317.
- 60 J.-X. Shen, J. M. Munro, M. K. Horton, P. Huck, S. Dwaraknath and K. A. Persson, *Sci. Data*, 2022, **9**, 661.
- 61 D. Liu, L. Jiang, D. Chen, Z. Hao, B. Deng, Y. Sun, X. Liu, B. Jia, L. Chen and H. Liu, *Chem. Eng. J.*, 2024, **482**, 149165.
- 62 B. He, Z. Wang, P. Xiao, T. Chen, J. Yu and L. Zhang, *Adv. Mater.*, 2022, **34**, 2203225.
- 63 C. Cheng, J. Zhang, B. Zhu, G. Liang, L. Zhang and J. Yu, *Angew. Chem., Int. Ed.*, 2023, **62**, e202218688.
- 64 X. Deng, J. Zhang, K. Qi, G. Liang, F. Xu and J. Yu, *Nat. Commun.*, 2024, **15**, 4807.
- 65 L. Li, C. Guo, T. Li, C. Yang, F. Chen, W. Wang, R. Yan, J. Ning and Y. Hu, *Appl. Surf. Sci.*, 2024, **651**, 159220.
- 66 J. Li, J. Guo, J. Zhang, Z. Sun and J. Gao, *Surf. Interfaces*, 2022, **34**, 102308.
- 67 L. Qi, M. Wang, J. Xue, Q. Zhang, F. Chen, Q. Liu, W. Li and X. Li, *Chem. – Eur. J.*, 2021, **27**, 14638–14644.
- 68 K. Huang, G. Liang, S. Sun, H. Hu, X. Peng, R. Shen and X. Li, *J. Mater. Sci. Technol.*, 2024, **193**, 98–106.
- 69 B. H. Park, H. Park, T. Kim, S. J. Yoon, Y. Kim, N. Son and M. Kang, *Int. J. Hydrogen Energy*, 2021, **46**, 38319–38335.
- 70 V. Soni, Sonu, P. Singh, S. Thakur, P. Thakur, T. Ahamad, V.-H. Nguyen, Q. Van Le, C. M. Hussain and P. Raizada, *J. Environ. Chem. Eng.*, 2023, **11**, 110856.
- 71 P. Mandyal, R. Sharma, S. Sambyal, N. Islam, A. Priye, M. Kumar, V. Chauhan and P. Shandilya, *J. Water Process Eng.*, 2024, **59**, 105008.
- 72 Q. Chen, L. Hu, Y. Shi, C. Liu, Y. Hou, J. Bi, J. C. Yu and L. Wu, *Chemosphere*, 2024, **352**, 141446.
- 73 W. Shi, J. C. Wang, A. Chen, X. Xu, S. Wang, R. Li, W. Zhang and Y. Hou, *Nanomaterials*, 2022, **12**, 2284.
- 74 D. Cui, S. Wang, X. Yang, L. Xu and F. Li, *Small*, 2024, **20**, 2306229.
- 75 L. Zhang, Y. Wu, N. Tsubaki and Z. Jin, *Acta Phys.-Chim. Sin.*, 2023, **39**, 2302051.
- 76 T. Ying, W. Liu, L. Yang, S. Zhang, Z. Wu, J. Li, R. Song, W. Dai, J. Zou and S. Luo, *Sep. Purif. Technol.*, 2024, **330**, 125272.
- 77 Z. Li, S. Ye, P. Qiu, X. Liao, Y. Yao, J. Zhang, Y. Jiang and S. Lu, *Dalton Trans.*, 2022, **51**, 10578–10586.
- 78 S. Arasavilli, P. A. Taksal, B. Kanti Das, S. Chowdhury and J. Bhattacharya, *J. Environ. Chem. Eng.*, 2024, **12**, 112703.
- 79 J. Huang, H. Shi, X. Wang, P. Wang, F. Chen and H. Yu, *Catal. Sci. Technol.*, 2024, **14**, 2514–2521.
- 80 D. Tang, D. Xu, Z. Luo, J. Ke, Y. Zhou, L. Li and J. Sun, *Nanomaterials*, 2022, **12**, 2455.
- 81 C. Yan, M. Xu, W. Cao, Q. Chen, X. Song, P. Huo, W. Zhou and H. Wang, *J. Environ. Chem. Eng.*, 2023, **11**, 111479.
- 82 M. Gao, W. Li, X. Su, Z. Li, X. Ding, X. Du, Y. Ren, H. Zhang, J. Feng and T. Wei, *Sep. Purif. Technol.*, 2023, **313**, 123447.
- 83 X. Yuan, J. Yang, Y. Yao, H. Shen, Y. Meng, B. Xie, Z. Ni and S. Xia, *Sep. Purif. Technol.*, 2022, **291**, 120965.
- 84 J. C. Wang, X. Qiao, W. Shi, J. He, J. Chen and W. Zhang, *Acta Phys.-Chim. Sin.*, 2023, **39**, 2210003.
- 85 L. Fan, J. Han, K. Wei, C. Ma, S. Feng, Y. Zhou, X. Dai, Z. Ye and Y. Wang, *J. Alloys Compd.*, 2023, **960**, 170382.
- 86 K. Huang, B. Feng, X. Wen, L. Hao, D. Xu, G. Liang, R. Shen and X. Li, *Chin. J. Struct. Chem.*, 2023, **42**, 100204.
- 87 J. Liu, F. Qi, N. Zhang, J. Yang, Z. Liang, C. Tian, W. Zhang, X. Tang, D. Wu and Q. Huang, *J. Mater. Sci.*, 2022, **57**, 15474–15487.
- 88 B. Dai, Y. Li, J. Xu, C. Sun, S. Li and W. Zhao, *Appl. Surf. Sci.*, 2022, **592**, 153309.
- 89 B. Dai, W. Zhao, W. Wei, J. Cao, G. Yang, S. Li, C. Sun and D. Y. C. Leung, *Carbon*, 2022, **193**, 272–284.
- 90 F. Mu, X. Miao, J. Cao, W. Zhao, G. Yang, H. Zeng, S. Li and C. Sun, *J. Cleaner Prod.*, 2022, **360**, 131948.
- 91 L. W. Wei, S. H. Liu and H. P. Wang, *ACS Appl. Mater. Interfaces*, 2023, **15**, 25473–25483.
- 92 J. Wang, S. Li, P. Ma, Z. Guo, Q. Ma, Q. Zhao, Y. Guo, J. Zhao and G. Guan, *Colloids Surf., A*, 2024, **690**, 133779.
- 93 P. Qiao, X. Wang, M. Dai, R. Piao, H. Liu, W. Wang, Y. Wang and H. Song, *Mater. Lett.*, 2024, **359**, 135923.
- 94 B. He, P. Xiao, S. Wan, J. Zhang, T. Chen, L. Zhang and J. Yu, *Angew. Chem., Int. Ed.*, 2023, **62**, e202313172.
- 95 L. Xu, H. L. An, X. Q. Wu, W. T. Ju, Y. Wang, X. F. Wang and X. Wang, *Surf. Interfaces*, 2023, **41**, 103202.
- 96 M. N. Gordon, K. Chatterjee, N. Christudas Beena and S. E. Skrabalak, *ACS Sustainable Chem. Eng.*, 2022, **10**, 15622–15641.
- 97 X. Wei, M. U. Akbar, A. Raza and G. Li, *Nanoscale Adv.*, 2021, **3**, 3353–3372.
- 98 J. Di, J. Xia, H. Li, S. Guo and S. Dai, *Nano Energy*, 2017, **41**, 172–192.
- 99 R. Suresh, S. Rajendran, P. S. Kumar, T. K. A. Hoang and M. Soto-Moscoco, *Environ. Res.*, 2022, **212**, 113149.
- 100 X. Dou, C. Zhang and H. Shi, *Sep. Purif. Technol.*, 2022, **282**, 120023.
- 101 S. S. Imam, R. Adnan and N. H. Mohd Kaus, *J. Environ. Chem. Eng.*, 2021, **9**, 105404.
- 102 X. Li, J. Xiong, X. Gao, J. Ma, Z. Chen, B. Kang, J. Liu, H. Li, Z. Feng and J. Huang, *J. Hazard. Mater.*, 2020, **387**, 121690.
- 103 K. Xie, S. Xu, K. Xu, W. Hao, J. Wang and Z. Wei, *Chemosphere*, 2023, **317**, 137823.
- 104 C. Y. Wang, X. Zhang and H. Q. Yu, *Coord. Chem. Rev.*, 2023, **493**, 215339.
- 105 X. Wei, M. U. Akbar, A. Raza and G. Li, *Nanoscale Adv.*, 2021, **3**, 3353–3372.
- 106 Y. Li, H. Jiang, X. Wang, X. Hong and B. Liang, *RSC Adv.*, 2021, **11**, 26855–26875.
- 107 Y. Song, X. Zheng, Y. Yang, Y. Liu, J. Li, D. Wu, W. Liu, Y. Shen and X. Tian, *Adv. Mater.*, 2024, **36**, 2305835.
- 108 Q. Zhong, Y. Li and G. Zhang, *Chem. Eng. J.*, 2021, **409**, 128099.



- 109 P. Kuang, J. Low, B. Cheng, J. Yu and J. Fan, *J. Mater. Sci. Technol.*, 2020, **56**, 18–44.
- 110 F. He, B. Zhu, B. Cheng, J. Yu, W. Ho and W. Macyk, *Appl. Catal., B*, 2020, **272**, 119006.
- 111 J. Low, L. Zhang, T. Tong, B. Shen and J. Yu, *J. Catal.*, 2018, **361**, 255–266.
- 112 J. Liu, F. Qi, N. Zhang, J. Yang, Z. Liang, C. Tian, W. Zhang, X. Tang, D. Wu and Q. Huang, *J. Mater. Sci.*, 2022, **57**, 15474–15487.
- 113 S. Sahani, K. Malika Tripathi, T. Il Lee, D. P. Dubal, C.-P. Wong, Y. Chandra Sharma and T. Young Kim, *Energy Convers. Manage.*, 2022, **252**, 115133.
- 114 C. M. Pelicano, J. Li, M. Cabrero-Antonino, I. F. Silva, L. Peng, N. V. Tarakina, S. Navalón, H. García and M. Antonietti, *J. Mater. Chem. A*, 2024, **12**, 475–482.
- 115 A. Garcia-Mulero, M. Cabrero-Antonino, H. García and A. Primo, *Sustainable Energy Fuels*, 2024, **8**, 1255–1259.
- 116 G. F. S. R. Rocha, M. A. R. da Silva, A. Rogolino, G. A. A. Diab, L. F. G. Noleto, M. Antonietti and I. F. Teixeira, *Chem. Soc. Rev.*, 2023, **52**, 4878–4932.
- 117 J. Liu, H. Wang and M. Antonietti, *Chem. Soc. Rev.*, 2016, **45**, 2308–2326.
- 118 J. Fu, J. Yu, C. Jiang and B. Cheng, *Adv. Energy Mater.*, 2018, **8**, 1701503.
- 119 X. Zhang, J. Yu, W. Macyk, S. Wageh, A. A. Al-Ghamdi and L. Wang, *Adv. Sustainable Syst.*, 2023, **7**, 2200113.
- 120 B. Dai, W. Zhao, W. Wei, J. Cao, G. Yang, S. Li, C. Sun and D. Y. C. Leung, *Carbon*, 2022, **193**, 272–284.
- 121 B. Dai, Y. Li, J. Xu, C. Sun, S. Li and W. Zhao, *Appl. Surf. Sci.*, 2022, **592**, 153309.
- 122 M. Sadat, A. Moghanlou, V. Rezvan, N. Tarighi and N. Sohrabi-Gilani, *Appl. Organomet. Chem.*, 2025, **39**, e7941.
- 123 X. Zhao, Y. Fan, W. Zhang, X. Zhang, D. Han, L. Niu and A. Ivaska, *ACS Catal.*, 2020, **10**, 6367–6376.
- 124 C. Hu, M. Li, J. Qiu and Y.-P. Sun, *Chem. Soc. Rev.*, 2019, **48**, 2315–2337.
- 125 Y. Bao and K. Chen, *Mol. Catal.*, 2017, **432**, 187–195.
- 126 A. E. Amooghini, H. Sanaeepur, R. Luque, H. Garcia and B. Chen, *Chem. Soc. Rev.*, 2022, **51**, 7427–7508.
- 127 S. Daliran, A. R. Oveisi, Y. Peng, A. López-Magano, M. Khajeh, R. Mas-Ballesté, J. Alemán, R. Luque and H. Garcia, *Chem. Soc. Rev.*, 2022, **51**, 7810–7882.
- 128 S. Navalón, A. Dhakshinamoorthy, M. Álvaro, B. Ferrer and H. García, *Chem. Rev.*, 2023, **123**, 445–490.
- 129 K.-G. Liu, F. Bigdeli, A. Panjehpour, A. Larimi, A. Morsali, A. Dhakshinamoorthy and H. Garcia, *Coord. Chem. Rev.*, 2023, **493**, 215257.
- 130 A. Dhakshinamoorthy, Z. Li, S. Yang and H. Garcia, *Chem. Soc. Rev.*, 2024, **53**, 3002–3035.
- 131 Z. Wang, X. Yue and Q. Xiang, *Coord. Chem. Rev.*, 2024, **504**, 215674.
- 132 Y. Wu, Y. Li, H. Li, H. Guo, Q. Yang and X. Li, *Sep. Purif. Technol.*, 2022, **303**, 122106.
- 133 Q. Zhao, J. Wang, Z. Li, Y. Guo, J. Wang, B. Tang, Y. Kansha, A. Yoshida, A. Abudula and G. Guan, *J. Photochem. Photobiol., A*, 2020, **399**, 112625.
- 134 A. A. Dubale, I. N. Ahmed, X. H. Chen, C. Ding, G. H. Hou, R.-F. Guan, X. Meng, X. L. Yang and M. H. Xie, *J. Mater. Chem. A*, 2019, **7**, 6062–6079.
- 135 H. Jiang, M. Xu, X. Zhao, H. Wang and P. Huo, *J. Environ. Chem. Eng.*, 2023, **11**, 109504.
- 136 H. Wu, X. Y. Kong, X. Wen, S.-P. Chai, E. C. Lovell, J. Tang and Y. H. Ng, *Angew. Chem., Int. Ed.*, 2021, **60**, 8455–8459.
- 137 X. Han, X. He, L. Sun, X. Han, W. Zhan, J. Xu, X. Wang and J. Chen, *ACS Catal.*, 2018, **8**, 3348–3356.
- 138 Y. Wu, X. Li, H. Zhao, F. Yao, J. Cao, Z. Chen, D. Wang and Q. Yang, *Chem. Eng. J.*, 2021, **426**, 131255.
- 139 H. Zhang, Y. Chen, Y. Pan, L. Bao and J. Yuan Ge, *J. Colloid Interface Sci.*, 2023, **642**, 470–478.
- 140 J. Du, Y. Hu, X. Wan, S. Tie, S. Lan and X. Gao, *Inorg. Chem.*, 2023, **62**, 9259–9271.
- 141 Z. Dong, J. Zhou, Z. Zhang, Y. Jiang, R. Zhou and C. Yao, *ACS Appl. Energy Mater.*, 2022, **5**, 10076–10085.
- 142 X. Bian, S. Zhang, Y. Zhao, R. Shi and T. Zhang, *InfoMat*, 2021, **3**, 719–738.
- 143 F. Temerov, Y. Baghdadi, E. Rattner and S. Eslava, *ACS Appl. Energy Mater.*, 2022, **5**, 14605–14637.
- 144 X. Fu, T. Ren, S. Jiao, Z. Tian, J. Yang and Q. Li, *J. Energy Chem.*, 2023, **83**, 397–422.
- 145 P. Raizada, A. Sudhaik, S. Patial, V. Hasija, A. A. Parwaz Khan, P. Singh, S. Gautam, M. Kaur and V.-H. Nguyen, *Arabian J. Chem.*, 2020, **13**, 8424–8457.
- 146 H. Hamad, M. M. Elsenety, W. Sadik, A.-G. El-Demerdash, A. Nashed, A. Mostafa and S. Elyamny, *Sci. Rep.*, 2022, **12**, 2217.
- 147 X. Liu, Y. Wu, Y. Li, X. Yang, Q. Ma and J. Luo, *Chem. Eng. J.*, 2024, **485**, 149855.
- 148 T. Han, H. Shi and Y. Chen, *J. Mater. Sci. Technol.*, 2024, **174**, 30–43.
- 149 D. Barman, J. Borah, S. Deb and B. K. Sarma, *Colloids Surf., A*, 2023, **663**, 131077.
- 150 T. Li, M. Li, J. Jiang, Z. Zhao, Z. Li, C. Zhao, X. Wang and S. Dong, *Appl. Catal., B*, 2023, **330**, 122539.
- 151 I. Ahmad, S. Shukrullah, M. Y. Naz, H. N. Bhatti, N. R. Khalid and S. Ullah, *Int. J. Hydrogen Energy*, 2023, **48**, 12683–12698.
- 152 B. Kakavandi, M. Moradi, F. Hasanvandian, A. Bahadoran, E. Mohebolkhames, M. Golshan, S. Ganachari and T. M. Aminabhavi, *Chem. Eng. J.*, 2024, **487**, 150399.
- 153 R. M. Mohamed and A. A. Ismail, *Ceram. Int.*, 2021, **47**, 9659–9667.
- 154 H. M. Alanazi, M. AlHaddad, A. Shawky and R. M. Mohamed, *J. Mater. Sci.: Mater. Electron.*, 2023, **34**, 1430.
- 155 M. Mahjoore, M. Honarmand and A. Aryafar, *Environ. Sci. Pollut. Res.*, 2023, **30**, 44439–44456.
- 156 R. M. Mohamed and A. Shawky, *J. Water Process Eng.*, 2024, **57**, 104612.
- 157 D. A. Sabit and S. E. Ebrahim, *Mater. Sci. Semicond. Process.*, 2023, **163**, 107559.
- 158 W. Shi, X. Qiao, J. Wang, M. Zhao, H. Ge, J. Ma, S. Liu and W. Zhang, *Nanomaterials*, 2022, **12**, 3247.
- 159 Y. Zhang, J. Li, W. Zhou, X. Liu, X. Song, S. Chen, H. Wang and P. Huo, *Appl. Catal., B*, 2024, **342**, 123449.



- 160 A. Mandal, G. Bhattacharya and K. Kargupta, *J. Mater. Res.*, 2024, **39**, 1935–1950.
- 161 J. Liu, J. Lin, K. Yi, F. Liu, F. Gao, M. Wang and F. Huang, *Nanoscale*, 2024, **16**, 6488–6494.
- 162 D. Meng, S. Gao, Z. Cheng, L. Wang, X. Hu, D. Gao, Q. Guo, X. Wang and M. Wang, *Opt. Mater.*, 2023, **143**, 114259.
- 163 T. D. Munusamy, S. Y. Chin and M. M. R. Khan, *Chemosphere*, 2022, **301**, 134649.
- 164 S. Parsaei, M. Rashid, A. Ghoorchian, K. Dashtian and D. Mowla, *Chem. Eng. J.*, 2023, **475**, 146448.
- 165 N. P. de Moraes, R. D. M. dos Santos, M. E. V. Gouvêa, A. de Siervo, R. da Silva Rocha, D. A. Reddy, Y. Lianqing, M. R. de Vasconcelos Lanza and L. A. Rodrigues, *Environ. Sci. Pollut. Res.*, 2023, **30**, 98211–98230.
- 166 S. Ali, A. Razzaq, H. Kim and S.-I. In, *Chem. Eng. J.*, 2022, **429**, 131579.
- 167 W. T. Alsaggaf, A. Shawky and M. H. H. Mahmoud, *Inorg. Chem. Commun.*, 2022, **143**, 109778.
- 168 K. Kannan, J. Gautam, D. Chanda, M. M. Meshesha, S. G. Jang and B. L. Yang, *Int. J. Hydrogen Energy*, 2023, **48**, 7273–7283.
- 169 B. M. Alajmi, A. S. Basaleh, A. A. Ismail and R. M. Mohamed, *Surf. Interfaces*, 2023, **39**, 102899.
- 170 M. Sayed, J. Yu, G. Liu and M. Jaroniec, *Chem. Rev.*, 2022, **122**, 10484–10537.
- 171 P. Kuang, M. Sayed, J. Fan, B. Cheng and J. Yu, *Adv. Energy Mater.*, 2020, **10**, 1903802.
- 172 X. Gao, H. Liu, D. Wang and J. Zhang, *Chem. Soc. Rev.*, 2019, **48**, 908–936.
- 173 B. Li, C. Lai, M. Zhang, G. Zeng, S. Liu, D. Huang, L. Qin, X. Liu, H. Yi, F. Xu, N. An and L. Chen, *Adv. Energy Mater.*, 2020, **10**, 2000177.
- 174 F. Xu, K. Meng, B. Zhu, H. Liu, J. Xu and J. Yu, *Adv. Funct. Mater.*, 2019, **29**, 1904256.
- 175 R. Chen, X. Dou, J. Xia, Y. Chen and H. Shi, *Sep. Purif. Technol.*, 2022, **296**, 121345.
- 176 X. Dou, Y. Chen and H. Shi, *Chem. Eng. J.*, 2022, **431**, 134054.
- 177 R. Li, F. Zhang, D. Wang, J. Yang, M. Li, J. Zhu, X. Zhou, H. Han and C. Li, *Nat. Commun.*, 2013, **4**, 1432.
- 178 H. Shi, Y. Li, X. Wang, H. Yu and J. Yu, *Appl. Catal., B*, 2021, **297**, 120414.
- 179 Z. H. Jabbar, B. H. Graimed, H. Hamzah Najm, S. H. Ammar and A. G. Taher, *J. Environ. Manage.*, 2023, **348**, 119302.
- 180 Q. Zhu, Q. Xu, M. Du, X. Zeng, G. Zhong, B. Qiu and J. Zhang, *Adv. Mater.*, 2022, **34**, 2202929.
- 181 L. Wang, B. Cheng, L. Zhang and J. Yu, *Small*, 2021, **17**, 2103447.
- 182 W. S. Rosa, L. G. Rabelo, L. G. Tiveron Zampaulo and R. V. Gonçalves, *ACS Appl. Mater. Interfaces*, 2022, **14**, 22858–22869.
- 183 M. Parastar Gharehlar, S. Sheshmani, F. R. Nikmaram and Z. Doroudi, *Sci. Rep.*, 2024, **14**, 4625.
- 184 S. Chandrasekaran, C. Bowen, P. Zhang, Z. Li, Q. Yuan, X. Ren and L. Deng, *J. Mater. Chem. A*, 2018, **6**, 11078–11104.
- 185 K. K. Kefeni and B. B. Mamba, *Sustainable Mater. Technol.*, 2020, **23**, e00140.
- 186 K. K. Kefeni and B. B. Mamba, *Sustainable Mater. Technol.*, 2020, **23**, e00140.
- 187 F. Li, X. Li, S. Tong, J. Wu, T. Zhou, Y. Liu and J. Zhang, *Nano Energy*, 2023, **117**, 108849.
- 188 R. Chen, J. Xia, Y. Chen and H. Shi, *Acta Phys.-Chim. Sin.*, 2023, **39**, 2209012.
- 189 J. Bao, X. Duan and P. Zhang, *J. Mater. Chem. A*, 2020, **8**, 24438–24444.
- 190 Q. Xiong, Q. Shi, X. Gu, X. Sheng, Y. Sun, H. Shi, L. Xu and G. Li, *J. Colloid Interface Sci.*, 2024, **654**, 1365–1377.
- 191 J. C. Wang, B. Wang, W. Shi, X. Qiao, X. Yang, L. Zhang, W. Zhang, R. Li and Y. Hou, *J. Environ. Chem. Eng.*, 2022, **10**, 108565.
- 192 B. Borjigin, L. Ding, C. Liu, H. Li and X. Wang, *Chem. Eng. J.*, 2024, **485**, 149995.
- 193 L. Zhang, Q. Shen, F. Huang, L. Jiang, J. Liu, J. Sheng, Y. Li and H. Yang, *Appl. Surf. Sci.*, 2023, **608**, 155064.
- 194 V. Dutta, A. Sudhaik, Sonu, P. Raizada, A. Singh, T. Ahamad, S. Thakur, Q. Van Le, V. H. Nguyen and P. Singh, *J. Mater. Sci. Technol.*, 2023, **162**, 11–24.
- 195 S. Wu, X. Yu, J. Zhang, Y. Zhang, Y. Zhu and M. Zhu, *Chem. Eng. J.*, 2021, **411**, 128555.
- 196 J. Liu, L. Huang, Y. Li, J. Yao, S. Shu, L. Huang, Y. Song and Q. Tian, *J. Colloid Interface Sci.*, 2022, **621**, 295–310.
- 197 V. Dutta, Sonu, A. Sudhaik, R. Kumar, P. Raizada, T. Ahamad, S. M. Alshehri, S. Thakur, Q. Van Le, S. Kaya, C. Hu, V. H. Nguyen and P. Singh, *J. Taiwan Inst. Chem. Eng.*, 2024, **156**, 105319.
- 198 W. Shi, J. C. Wang, X. Guo, X. Qiao, F. Liu, R. Li, W. Zhang, Y. Hou and H. Han, *Nano Res.*, 2022, **15**, 5962–5969.
- 199 C. Akshhaya, M. K. Okla, A. A. AL-ghamdi, M. A. Abdel-Maksoud, H. AbdElgawad, A. Das and S. S. Khan, *Surf. Interfaces*, 2021, **27**, 101523.
- 200 D. Liu, L. Jiang, D. Chen, Z. Hao, B. Deng, Y. Sun, X. Liu, B. Jia, L. Chen and H. Liu, *Chem. Eng. J.*, 2024, **482**, 149165.
- 201 D. Majhi, A. Kumar Mishra, K. Das, R. Bariki and B. G. Mishra, *Chem. Eng. J.*, 2021, **413**, 127506.
- 202 J. X. Mao, J. C. Wang, H. Gao, W. Shi, H. P. Jiang, Y. Hou, R. Li, W. Zhang and L. Liu, *Int. J. Hydrogen Energy*, 2022, **47**, 8214–8223.
- 203 W. Shi, J. C. Wang, X. Guo, H. L. Tian, W. Zhang, H. Gao, H. Han, R. Li and Y. Hou, *J. Alloys Compd.*, 2021, **890**, 161919.
- 204 L. Wang, Y. Xue, G. Yang, X. Liu, W. He, M. Zhang and Z. Liu, *Sep. Purif. Technol.*, 2023, **317**, 123856.
- 205 V. Dutta, S. Sonu, P. Raizada, V. K. Thakur, T. Ahamad, S. Thakur, P. Kumar Verma, H. H. P. Quang, V. H. Nguyen and P. Singh, *Environ. Sci. Pollut. Res.*, 2023, **30**, 124530.
- 206 J. Luo, X. Zhou, F. Yang, X. Ning, L. Zhan, Z. Wu and X. Zhou, *J. Cleaner Prod.*, 2022, **357**, 131992.
- 207 J. Qu, D. Zhang, Y. Li, P. Wang, Y. Mao, T. Zhang, S. Zhan and Y. Li, *Appl. Catal., B*, 2024, **340**, 123246.
- 208 X. Wang, N. Su, X. Wang, D. Cao, C. Xu, X. Wang, Q. Yan, C. Lu and H. Zhao, *J. Colloid Interface Sci.*, 2024, **661**, 943–956.
- 209 A. Sudhaik, P. Raizada, S. Rangabhashiyam, A. Singh, V.-H. Nguyen, Q. Van Le, A. A. P. Khan, C. Hu, C.-W. Huang, T. Ahamad and P. Singh, *Surf. Interfaces*, 2022, **33**, 102182.



- 210 P. Chen, P. Zhang, Y. Cui, X. Fu and Y. Wang, *Mater. Today Sustainable*, 2023, **21**, 100276.
- 211 A. Rahman and M. M. Khan, *New J. Chem.*, 2021, **45**, 19622–19635.
- 212 S. N. F. Moridon, K. Arifin, R. M. Yunus, L. J. Minggu and M. B. Kassim, *Ceram. Int.*, 2022, **48**, 5892–5907.
- 213 C. Coughlan, M. Ibáñez, O. Dobrozhan, A. Singh, A. Cabot and K. M. Ryan, *Chem. Rev.*, 2017, **117**, 5865–6109.
- 214 Y. Sun, K. Lai, N. Li, Y. Gao and L. Ge, *Appl. Catal., B*, 2024, **357**, 124302.
- 215 Y. Wang, M. Liu, C. Wu, J. Gao, M. Li, Z. Xing, Z. Li and W. Zhou, *Small*, 2022, **18**, 2202544.
- 216 Y. Zhang, H. Shi, S. Zhao, Z. Chen, Y. Zheng, G. Tu, S. Zhong, Y. Zhao and S. Bai, *Small*, 2024, **20**, 2304050.
- 217 Y. Sun, R. Xiong, X. Ke, J. Liao, Y. Xiao, B. Cheng and S. Lei, *Sep. Purif. Technol.*, 2024, **345**, 127253.
- 218 G. Wang, Y. Quan, K. Yang and Z. Jin, *J. Mater. Sci. Technol.*, 2022, **121**, 28–39.
- 219 S. Shen, Y. Chu, Y. Xu, X. Liu, H. Xiu, J. Li, Z. Tang, J. Xu and S. Xiao, *Int. J. Hydrogen Energy*, 2024, **61**, 734–742.
- 220 K. Dong, H. Li, C. Zhang, M. Zhou, Q. Liang, Y. Wang, Z. Li and S. Xu, *Int. J. Hydrogen Energy*, 2024, **51**, 1357–1365.
- 221 L. Zhang, X. Wang, Y. Li and Z. Jin, *Catal. Sci. Technol.*, 2023, **13**, 3667–3681.
- 222 Z. Ma, W. Guo, K. Zhang, N. Wang, Z. Li and J. Li, *Molecules*, 2023, **28**, 3084.
- 223 S. Panda, R. Bariki, S. K. Pradhan, S. K. Nayak and B. G. Mishra, *ACS Appl. Nano Mater.*, 2024, **7**, 7365–7380.
- 224 Y. Wang, Q. Liu, N. H. Wong, J. Sunarso, J. Huang, G. Dai, X. Hou and X. Li, *Ceram. Int.*, 2022, **48**, 2459–2469.
- 225 J. W. Wang, W. Chen, D. M. Han and J. R. Chen, *Opt. Mater.*, 2023, **138**, 113635.
- 226 C. Liu, X. He, Q. Xu and M. Chen, *J. Hazard. Mater.*, 2023, **445**, 130551.
- 227 F. Chen, J. Y. Liao, X. Lu, Y. Z. Xu, X. H. Jiang and M. Tian, *Appl. Surf. Sci.*, 2023, **621**, 156721.
- 228 X. Xiang, M. Zhang, Q. Huang, Y. Mao, J. Jia, X. Zeng, Y. Dong, J. Liao, X. Chen, X. Yao, Q. Zheng and W. Chen, *Chemosphere*, 2024, **352**, 141351.
- 229 Y. Zhang, X. Chen, Y. Ye and J. Chen, *J. Catal.*, 2023, **419**, 9–18.
- 230 T. Wang and Z. Jin, *J. Mater. Chem. C*, 2023, **11**, 13957–13970.
- 231 W. Zhao, S. Liu, Y. Liu, S. Yang, B. Liu, X. Hong, J. Shen and C. Sun, *J. Colloid Interface Sci.*, 2024, **654**, 134–149.
- 232 J. Peng, Y. Han, D. Ma, R. Zhao, J. Han and L. Wang, *Renewable Energy*, 2023, **212**, 984–993.
- 233 Z. Li, D. Lan, Z. Li, J. Sun, S. Chen, J. Yang, J. Wei, Z. Yu, S. Wang and Y. Hou, *Chemosphere*, 2022, **301**, 134684.
- 234 A. Moghaddam Saray, H. Azimi, A. Shirmardi, M. Nouri and R. Yousefi, *Surf. Interface*, 2023, **42**, 103416.
- 235 K. Wang, Z. Luo, B. Xiao, T. Zhou, J. Zhao, C. Shen, D. Li, Z. Qiu, J. Zhang, T. He and Q. Liu, *J. Colloid Interface Sci.*, 2023, **652**, 1908–1916.
- 236 L. Shi, J. Yin, Y. Liu, H. Liu, H. Zhang and H. Tang, *Chemosphere*, 2022, **309**, 136607.
- 237 J. Y. Tian, W. C. Lv, A. S. Shen, Y. Ma, M. Wang, S. Zhang, X. L. Liu, Z. Zhang and M. Du, *Sep. Purif. Technol.*, 2023, **327**, 124903.
- 238 W. Zhang, K. Wei, L. Fan, Z. Song, H. Han, Q. Wang, S. Song, D. Liu and S. Feng, *Int. J. Hydrogen Energy*, 2024, **59**, 551–560.
- 239 Y. Cao, G. Wang, H. Liu, Y. Li, Z. Jin and Q. Ma, *Int. J. Hydrogen Energy*, 2021, **46**, 7230–7240.
- 240 P. Zhu, C. Feng, Q. Liang, M. Zhou, Z. Li and S. Xu, *Ceram. Int.*, 2023, **49**, 20706–20714.
- 241 N. Zhang, Y. G. Luo, Y. H. Chen, J. Y. Zhang, H. Wang and Z. J. Liu, *ACS Sustainable Chem. Eng.*, 2023, **11**, 4813–4824.
- 242 H. Hu, X. Zhang, K. Zhang, Y. Ma, H. Wang, H. Li, H. Huang, X. Sun and T. Ma, *Adv. Energy Mater.*, 2024, **14**, 2303638.
- 243 S. K. Han, C. Gu, S. Zhao, S. Xu, M. Gong, Z. Li and S. H. Yu, *J. Am. Chem. Soc.*, 2016, **138**, 12913–12919.
- 244 L. Jiang, K. Wang, X. Wu and G. Zhang, *Solar RRL*, 2021, **5**, 2000326.
- 245 S. Sun, P. Li, S. Liang and Z. Yang, *Nanoscale*, 2017, **9**, 11357–11404.
- 246 R. Mohammed, M. E. M. Ali, E. Gomaa and M. Mohsen, *Sci. Rep.*, 2022, **12**, 18153.
- 247 Z. Ma, W. Guo, K. Zhang, N. Wang, Z. Li and J. Li, *Molecules*, 2023, **28**, 3084.
- 248 K. Dong, H. Li, C. Zhang, M. Zhou, Q. Liang, Y. Wang, Z. Li and S. Xu, *Int. J. Hydrogen Energy*, 2024, **51**, 1357–1365.
- 249 H. Ding, D. Han, Y. Han, Y. Liang, X. Liu, Z. Li, S. Zhu and S. Wu, *J. Hazard. Mater.*, 2020, **393**, 122423.
- 250 D. C. Onwudiwe, O. C. Olatunde, V. M. Nkwe, Y. Ben Smida and H. Ferjani, *Inorg. Chem. Commun.*, 2023, **155**, 111075.
- 251 M. Sayed, F. Xu, P. Kuang, J. Low, S. Wang, L. Zhang and J. Yu, *Nat. Commun.*, 2021, **12**, 4936.
- 252 A. Meng, B. Cheng, H. Tan, J. Fan, C. Su and J. Yu, *Appl. Catal., B*, 2021, **289**, 120039.
- 253 L. Zhang, B. Zhu, D. Xu, Z. Qian, P. Xie, T. Liu and J. Yu, *J. Mater. Sci. Technol.*, 2024, **172**, 185–195.
- 254 Z. Wang, Y. Chen, L. Zhang, B. Cheng, J. Yu and J. Fan, *J. Mater. Sci. Technol.*, 2020, **56**, 143–150.
- 255 C. Bie, B. Zhu, F. Xu, L. Zhang and J. Yu, *Adv. Mater.*, 2019, **31**, 1902868.
- 256 X. Song, X. Shan, H. Xue, X. Li, R. Liu, J. Kong, Z. Zuo, X. Su, Q. Zhang, Y. Yin and Y. Cai, *ACS Appl. Nano Mater.*, 2024, **7**, 26489–26514.
- 257 J. Zhang, H. Chen, X. Duan, H. Sun and S. Wang, *Mater. Today*, 2023, **68**, 234–253.
- 258 C. Song, Z. Wang, Z. Yin, D. Xiao and D. Ma, *Chem. Catal.*, 2022, **2**, 52–83.
- 259 J. Li, L. Ding, Z. Su, K. Li, F. Fang, R. Sun, Y. Qin and K. Chang, *Adv. Mater.*, 2023, **35**, 2305535.
- 260 Y. C. Liu, X. Liu, G. H. Zhang, W. Liu, J. Q. Wang, X. Wang, C. L. Chen, Y. Wang and Z. Xiang, *Environ. Res.*, 2023, **216**, 114720.
- 261 D. Guo, S. Jiang, L. Shen, E. Y. B. Pun and H. Lin, *Small*, 2024, **20**, 2401335.
- 262 A. Shamloufard, S. Hajati, A. A. Youzbashi, K. Dashtian, M. Moradi and J. Toth, *Appl. Surf. Sci.*, 2022, **590**, 153118.
- 263 Q. Guo, Y. Yao, Z.-C. Luo, Z. Qin, G. Xie, M. Liu, J. Kang, S. Zhang, G. Bi, X. Liu and J. Qiu, *ACS Nano*, 2016, **10**, 9463–9469.



- 264 J. Di and W. Jiang, *Mater. Today Catal.*, 2023, **1**, 100001.
- 265 F. Xu, J. Zhang, B. Zhu, J. Yu and J. Xu, *Appl. Catal., B*, 2018, **230**, 194–202.
- 266 F. Deng, X. Lu, Y. Luo, J. Wang, W. Che, R. Yang, X. Luo, S. Luo and D. D. Dionysiou, *Chem. Eng. J.*, 2019, **361**, 1451–1461.
- 267 W. Yang, G. Ma, Y. Fu, K. Peng, H. Yang, X. Zhan, W. Yang, L. Wang and H. Hou, *Chem. Eng. J.*, 2022, **429**, 132181.
- 268 J. Chen, W. Mu and C. Chang, *Environ. Pollut.*, 2024, **351**, 124077.
- 269 J. Zhang, Y. Zhao, K. Qi and S. Yuan Liu, *J. Mater. Sci. Technol.*, 2024, **172**, 145–155.
- 270 J. Luo, Z. Lin, Y. Zhao, S. Jiang and S. Song, *Chin. J. Catal.*, 2020, **41**, 122–130.
- 271 Y. Zhu, L. Peng, Z. Fang, C. Yan, X. Zhang and G. Yu, *Adv. Mater.*, 2018, **30**, 1706347.
- 272 F. Xu, Y. He, J. Zhang, G. Liang, C. Liu and J. Yu, *Angew. Chem., Int. Ed.*, 2025, **64**, e202414672.
- 273 Y. Xia, H. Yang, W. Ho, B. Zhu and J. Yu, *Appl. Catal., B*, 2024, **344**, 123604.
- 274 B. Sun, Z. Liang, Y. Qian, X. Xu, Y. Han and J. Tian, *ACS Appl. Mater. Interfaces*, 2020, **12**, 7257–7269.
- 275 Z. Wang, M. Xiao, J. You, G. Liu and L. Wang, *Acc. Mater. Res.*, 2022, **3**, 1127–1136.
- 276 D. Maarisetty and S. S. Baral, *J. Mater. Chem. A*, 2020, **8**, 18560–18604.
- 277 S. Bai, N. Zhang, C. Gao and Y. Xiong, *Nano Energy*, 2018, **53**, 296–336.
- 278 J. Xue, M. Fujitsuka and T. Majima, *ACS Appl. Mater. Interfaces*, 2019, **11**, 40860–40867.
- 279 W. Zhao, J.-H. Cao, J.-J. Liao, Y. Liu, X.-J. Zeng, J.-Y. Shen, X.-K. Hong, Y. Guo, H.-H. Zeng and Y.-Z. Liu, *Rare Met.*, 2024, **43**, 3118–3133.
- 280 S. Wang, D. Zhang, P. Su, X. Yao, J. Liu, X. Pu, H. Li and P. Cai, *J. Colloid Interface Sci.*, 2023, **650**, 825–835.
- 281 A. Chawla, A. Sudhaik, Sonu, R. Kumar, P. Raizada, A. A. P. Khan, T. Ahamad, V.-H. Nguyen, R. Selvasembian, A. Kaushik and P. Singh, *J. Environ. Chem. Eng.*, 2024, **12**, 113125.
- 282 Z. Pu, T. Liu, I. S. Amiin, R. Cheng, P. Wang, C. Zhang, P. Ji, W. Hu, J. Liu and S. Mu, *Adv. Funct. Mater.*, 2020, **30**, 2004009.
- 283 H. Zhou, R. Chen, C. Han, P. Wang, Z. Tong, B. Tan, Y. Huang and Z. Liu, *J. Colloid Interface Sci.*, 2022, **610**, 126–135.
- 284 R. Shen, J. Xie, X. Lu, X. Chen and X. Li, *ACS Sustainable Chem. Eng.*, 2018, **6**, 4026–4036.
- 285 W. Wang, X. Zhao, Y. Cao, Z. Yan, R. Zhu, Y. Tao, X. Chen, D. Zhang, G. Li and D. L. Phillips, *ACS Appl. Mater. Interfaces*, 2019, **11**, 16527–16537.
- 286 X. Li, T. Han, Y. Zhou, M. Wang, Z. Tian, F. Deng, Y. Luo, Y. Xie, J. Huang, L. Han, Z. Chen, Z. Feng and W. Chen, *Appl. Catal., B*, 2024, **350**, 123913.
- 287 D. J. Li, J. Kang, H. J. Lee, D. S. Choi, S. H. Koo, B. Han and S. O. Kim, *Adv. Energy Mater.*, 2018, **8**, 1702806.
- 288 Z. Wu, X. Li, W. Liu, Y. Zhong, Q. Gan, X. Li and H. Wang, *ACS Catal.*, 2017, **7**, 4026–4032.
- 289 X. Zhang, D. Kim, J. Yan and L. Y. S. Lee, *ACS Appl. Mater. Interfaces*, 2021, **13**, 9762–9770.
- 290 X. Zhang, K.-A. Min, W. Zheng, J. Hwang, B. Han and L. Y. S. Lee, *Appl. Catal., B*, 2020, **273**, 118927.
- 291 W. Zhu, Z. Xia, B. Shi and C. Lü, *Langmuir*, 2023, **39**, 15665–15675.
- 292 H. Yuan, B. Cheng, J. Lei, L. Jiang and Z. Han, *Nat. Commun.*, 2021, **12**, 1835.
- 293 J. Su, G. D. Li, X. H. Li and J. S. Chen, *Adv. Sci.*, 2019, **6**, 1801702.
- 294 R. Shen, L. Zhang, X. Chen, M. Jaroniec, N. Li and X. Li, *Appl. Catal., B*, 2020, **266**, 118619.
- 295 J. Ran, W. Guo, H. Wang, B. Zhu, J. Yu and S. Z. Qiao, *Adv. Mater.*, 2018, **30**, 1800128.
- 296 Q. Xu, B. Zhu, C. Jiang, B. Cheng and J. Yu, *Solar RRL*, 2018, **2**, 1800006.
- 297 M. Liu, J. Wen, R. Xiao, R. Tan, Y. Qin, J. Li, Y. Bai, M. Xi, W. Yang, Q. Fang, L. Hu, W. Gu and C. Zhu, *Nano Lett.*, 2023, **23**, 5358–5366.
- 298 J. Qiu, K. Meng, Y. Zhang, B. Cheng, J. Zhang, L. Wang and J. Yu, *Adv. Mater.*, 2024, **36**, 2400288.
- 299 Y. He, P. Hu, J. Zhang, G. Liang, J. Yu and F. Xu, *ACS Catal.*, 2024, **14**, 1951–1961.
- 300 Y. Yang, J. Liu, M. Gu, B. Cheng, L. Wang and J. Yu, *Appl. Catal., B*, 2023, **333**, 122780.
- 301 G. Sun, J. Zhang, B. Cheng, H. Yu, J. Yu and J. Xu, *Chem. Eng. J.*, 2023, **476**, 146818.

