


Cite this: *Nanoscale Adv.*, 2024, 6, 4137

Cesium lead bromide perovskite nanocrystals synthesized *via* supersaturated recrystallization at room temperature: comparison of one-step and two-step processes†

Dula Adugna Idosa,^{ab} Muluaalem Abebe,^a Dhakshnamoorthy Mani,^a
Jibin Keloth Paduvilan,^c Lishin Thottathi,^d Aparna Thankappan,^e Sabu Thomas^f
and Jung Yong Kim ^{*gh}

Over more than a decade, lead halide perovskites (LHPs) have been popular as a next-generation semiconductor for optoelectronics. Later, all-inorganic CsPbX₃ (X = Cl, Br, and I) nanocrystals (NCs) were synthesized *via* supersaturated recrystallization (SR) at room temperature (RT). However, compared to the hot injection (HI) method, the formation mechanism of NCs *via* SR-RT has not been well studied. Hence, this study will contribute to elucidating SR-RT based on the LaMer model and Hansen solubility parameter. Herein, we also demonstrate the entropy-driven mixing between two dissimilar polar-nonpolar (DMF–toluene) solvents. Next, we find that, in a poor solvent (toluene \gg DMF in volume), \sim 60 nm sized CsPbBr₃ NCs were synthesized in one step, whereas in a marginal solvent (toluene \approx DMF), \sim 3.5 nm sized NCs were synthesized in two steps, indicating the importance of solvent polarity, specifically the ‘solubility parameter’. In addition, in the presence of a CuBr₂ additive, high-quality cubic NCs (with \sim 3.8 nm and \sim 21.4 nm edge sizes) were synthesized. Hence, through this study, we present a ‘solubility parameter-based nanocrystal-size control model’ for SR-RT processes.

Received 21st May 2024
Accepted 17th June 2024

DOI: 10.1039/d4na00423j

rsc.li/nanoscale-advances

1. Introduction

All-inorganic cesium lead halide perovskite (LHP) (CsPbX₃, X = Cl, Br, and I) nanocrystals (NCs), also called quantum dots (QDs) in the case of zero dimension (0D), have received increasing attention as emerging semiconductors in next-generation optoelectronic devices, including light emitting diodes (LEDs), solar cells, photodetectors,^{1,2} field-effect transistors (FETs),³ lasers, sensors,^{4,5} and quantum communication elements.⁶ Specifically, high color purity and high quantum efficiency make CsPbX₃ NCs highly competitive for wide color

gamut display applications.^{7–10} In addition to their outstanding luminescence performance, CsPbX₃ NCs offer the advantage of tunable energy bands through chemical and morphology modulation.¹¹

Green-emitting CsPbBr₃ NCs were tuned to a blue emitter by adjusting the stoichiometry of halide (bromide and chloride) anions.^{12,13} However, LHP NCs with mixed halides are known to have drawbacks such as low defect tolerance of chlorine anions and phase instability upon exposure to light and/or voltage when applied as a blue light source in lighting and display technology.¹³ The other strategy for blue-emitting LHP NCs relies on the quantum confinement effect, a unique property of low-dimensional semiconductors. For example, strongly quantum-confined CsPbBr₃ NCs, such as dots, nanowires, nanoplatelets, and nanocubes, have been demonstrated as blue emitters.^{10,14–17} However, the fast nucleation and growth rate of CsPbBr₃ NCs, originating from their low particle formation energy and soft ionic lattice structure, makes it difficult to control the size and morphology of NCs in the highly quantum confined region.¹⁸

To address the precise control of the size and shape of LHP NCs, several processing methods such as ‘hot-injection (HI)’, ‘ligand-assisted reprecipitation (LARP)’, and ‘room-temperature (RT) supersaturated recrystallization (SR)’ have been employed.^{10,19,20} For example, Kovalenko and coworkers

^aFaculty of Materials Science and Engineering, Jimma Institute of Technology, Jimma University, P. O. Box 378, Jimma, Ethiopia

^bDepartment of Physics, College of Natural and Computational Science, Mizan-Tepi University, P. O. Box 260, Mizan, Ethiopia

^cSchool of Chemical Sciences, Mahatma Gandhi University, Kottayam 686560, India

^dDepartment of Physics and Mathematics, Università Cattolica del Sacro Cuore, Via della Garzetta, 48, 25133 Brescia, BS, Italy

^eDepartment of Physics, Baselius College, Kottayam 686001, India

^fSchool of Energy Materials, Mahatma Gandhi University, Kottayam 686560, India

^gDepartment of Materials Science and Engineering, Adama Science and Technology University, P. O. Box 1888, Adama, Ethiopia. E-mail: jungyong.kim@astu.edu.et

^hCenter of Advanced Materials Science and Engineering, Adama Science and Technology University, P. O. Box 1888, Adama, Ethiopia

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4na00423j>

controlled the size of CsPbX₃ NCs in the range of 4–15 nm edge lengths by varying the reaction temperature from 200 to 140 °C in 2015.¹⁰ Rogach *et al.* demonstrated the size-tuned bandgap of CH₃NH₃PbBr₃ NCs by varying the precipitation temperature from 0 to 60 °C *via* LARP routes.¹⁹ Later, in 2016, Zeng and coworkers invented an RT-SR (a special case of LARP) method for the synthesis of CsPbX₃ NCs within a few seconds at ambient conditions without any inert gas and local injection operation.²⁰ Furthermore, ligand composition and LHP precursor concentration were varied to control the size of the NCs.^{21,22} Son *et al.* accurately controlled the CsPbX₃ NC size with high ensemble uniformity utilizing thermodynamic equilibrium.¹⁸ Pradhan *et al.* reported the precise step-growth process of CsPbBr₃ NCs *via* unit cell size (~0.6 nm) increment.¹⁶ Zhang *et al.* demonstrated the size and shape control of LHP NCs using suitable amounts of water, contrary to the common preconception that LHPs may rapidly decompose when exposed to polar solvents such as water.²³ Interestingly, Yang *et al.* achieved the controlled synthesis of ~3 nm sized CsPbBr₃ NCs using the cryogenic temperature synthetic strategy.²⁴ Moreover, the quantum-confinement effect is further tunable by using copper, nickel, tin, cadmium, zinc, and aluminum ions as an additive (dopant) for CsPbX₃ NCs.^{25–28}

The nucleation and growth processes of LHP^{29,30} and cadmium chalcogenide (CdX, X = S, Se, and Te)^{31,32} NCs have been interpreted based on the classical LaMer model introduced in the 1950s.^{33,34} However, studies on the formation mechanism of colloidal NCs have been mostly focused on the popular HI^{10,35} and heat-up^{31,32} processes instead of the SR (LARP)^{19,20,36} method operating at RT. Hence, this work is dedicated to elucidating the NC formation mechanism for the green- and blue-emitting CsPbBr₃ NCs synthesized *via* one-step and two-step SR processes at RT, respectively. For this purpose, we additionally employ, for the first time, the Hildebrand and Hansen solubility parameters³⁷ determining the NC size (green or blue emitter) through the balance between the formation and dissolution of CsPbBr₃ NCs in solvent medium – good (polar), marginal (partially polar) or poor (nonpolar). We find that the partially-polar marginal solvent medium is suitable for blue-emitting NCs whereas the nonpolar poor solvent quality is acceptable for green-emitting NCs. Furthermore, to understand the solvent–antisolvent (*e.g.*, the binary DMF–toluene system) miscibility, we employ the Flory–Huggins theory^{38,39} predicting the entropy-driven mixing between two dissimilar polar–nonpolar solvents, enabling the SR routes using solvent–antisolvent engineering for the synthesis of CsPbBr₃ NCs at RT.

2. Materials and methods

2.1. Chemicals

Cesium bromide (CsBr, 99.9%, Sigma-Aldrich, Darmstadt, Germany), lead(II) bromide (PbBr₂, 99.0%, AR chemicals, Delhi, India), copper(II) bromide (CuBr₂, 99.9% Sigma-Aldrich, Darmstadt, Germany), oleic acid (OA, 98%, Sigma-Aldrich, Darmstadt, Germany), oleylamine (OAm, technical grade 70%, Sigma-Aldrich, Darmstadt, Germany), *N,N*-dimethylformamide (DMF,

99%, SRL, Mumbai, India), toluene (99%, Loba Chemie, Mumbai), and ethyl acetate (EA, 99%, SRL, Mumbai, India) were used as received without further purification.

2.2. Synthesis of CsPbBr₃ NCs: one-step process

The precursor solution was prepared by dissolving PbBr₂ (0.2 mmol), CsBr (0.2 mmol), OA (0.5 mL), and OAm (0.25 mL) in DMF (5 mL) under stirring for 2 hours at room temperature. Then, 1 mL of the solution was added to 10 mL toluene (*i.e.*, toluene ≫ DMF in volume) under vigorous stirring. Immediately, the formation of CsPbBr₃ NCs was verified with a bright green-light emission in the solution under a 365 nm UV lamp.

2.3 Synthesis of CsPbBr₃ NCs: two-step process

The precursor solution was prepared by dissolving PbBr₂ (0.2 mmol), CsBr (0.2 mmol), OA (0.5 mL), and OAm (0.25 mL) in DMF (5 mL) under stirring for 2 hours at room temperature. Then, 5 mL of toluene was added to the 5 mL solution (toluene ≈ DMF in volume) under vigorous stirring to obtain the first stage of crystallization. Then, after aging for 2 min, 1 mL of the solution was added to 10 mL toluene (toluene ≫ DMF) to finalize the crystallization – the second stage in the two-step process. Immediately, the formation of CsPbBr₃ NCs was verified with a bright blue-light emission in the solution under a 365 nm UV lamp. Note that all the synthesis reactions were carried out without any inert gas in the air.

2.4. Purification

For comparison purposes, the solutions of both NCs synthesized by one-step and two-step processes were centrifuged at 9000 rpm for 5 min, and the precipitates were collected and characterized. In this report, for the two-step synthesis, the precipitant is referred to as the unpurified CsPbBr₃ NCs. To purify the NCs synthesized by two steps, the solution was first centrifuged at 3500 rpm to separate larger NCs and/or aggregation as precipitate and smaller ones as supernatant. The supernatant was collected and further centrifuged at 8500 rpm for 10 min to separate NCs from the solution, and the NCs are referred to as the purified CsPbBr₃ NCs in this report. Finally, the supernatant was discarded, and the precipitate was dispersed in toluene for further characterization. In this study, CsPbBr₃ NCs synthesized *via* the one-step process were used without further purification.

2.5. Characterization

The ultraviolet-visible (UV-Vis) absorption spectra of as-prepared NCs in toluene solution were obtained using the P9 UV-Vis spectrophotometer, China. The luminescence of NCs was recorded by the Cary Eclipse Fluorescence spectrophotometer, Malaysia. The crystal structure of the NCs was examined by X-ray diffraction (XRD) with Cu K α radiation, $\lambda = 1.5406$ Å at 30 kV and 25 mA (Drawell XRD 7000, China). The morphology and microstructure as prepared NCs were analyzed by high-resolution transmission electron microscopy (HR-TEM)



(JEOL JEM-2100; Peabody, MA, USA) with an operating voltage of 200 kV.

2.6. Computational details

In order to understand the electronic structures of CsPbBr₃ perovskite, the density functional theory (DFT)-based first-principle calculations as in the Quantum ESPRESSO package were carried out.⁴⁰ The generalized gradient approximation (GGA) functional of Perdew–Burke–Ernzerhof for solids (PBEsol) is used to describe the exchange–correlation potential.^{41,42} The interactions between the atomic core and the valence electrons were described by the ultrasoft pseudopotentials. The valence electronic configurations for Cs, Pb, and Br atoms are 5s²5p⁶6s¹, 5d¹⁰6s²6p² and 4s²4p⁵, respectively. A plane wave cut off 38 Ry and 7 × 7 × 7 *k*-point mesh was used in the calculation process. Accordingly, the electronic band structure and the projected density of state (PDOS) of CsPbBr₃ are summarized and displayed in Fig. S1 in ESI.†

3. Results and discussion

Fig. 1 shows a schematic representation of the quantum confinement effect, *e.g.*, size-dependent light emission, of CsPbBr₃ NCs. This phenomenon is observable when the electron and hole wave functions are reduced to be smaller than the excitonic Bohr radius, *e.g.*, ~7 nm for CsPbBr₃.^{10,43–45} Specifically, when the size of CsPbBr₃ NCs is less than ~4 nm, the pure blue emission could be expected.⁴⁶ Hence, this study focuses on the processing-nanostructure-optical property relationship of these CsPbBr₃ NCs with emphasis on the formation mechanism of green- and blue-emitting CsPbBr₃ NCs *via* the SR method at RT.

Briefly, in the LaMer model (Fig. 2a),^{33,34} the total free energy (ΔG) for the formation of a spherical particle with radius *r* could be expressed as

$$\Delta G = 4\pi r^2 \gamma + \frac{4}{3}\pi r^3 \Delta G_V \quad (1)$$

where γ is the solid/liquid interfacial energy per unit area and ΔG_V is the volume free energy. Here, ΔG_V can be expressed as

$-k_B T \ln S/V$, where k_B , *T*, and *V* are Boltzmann constant, temperature, and the volume of monomer (*e.g.*, Cs[PbBr₃] aggregate or precursor ions/complexes in this study), respectively. Thus, the degree of supersaturation (*S*) is the driving force for the reduction of ΔG_V . Under unstable equilibrium, $\partial \Delta G / \partial r = 0$, the critical radius is $r_c = -2\gamma / \Delta G_V = 2\gamma V_m / RT \ln S$ and concomitantly, the total free energy $\Delta G(r = r_c)$ is $\Delta G_c = 16\pi\gamma^3 / 3\Delta G_V^2 = 16\pi\gamma^3 V^2 / [3k_B^2 T^2 (\ln S)^2]$. Then, the nucleation rate (*dN/dt*) could be defined as follows,^{31,32}

$$\frac{dN}{dt} = A \exp\left(-\frac{\Delta G_c}{k_B T}\right) = A \exp\left(-\frac{16\pi\gamma^3 V^2}{3k_B^3 T^3 (\ln S)^2}\right) \quad (2)$$

which describes that the burst nucleation is largely governed by the degree of supersaturation (*S*) and interfacial energy (γ) in the case of SR at RT (constant temperature). Here, *A* is a pre-factor. Importantly, the factor *S* can be controlled by the amount of nonpolar antisolvent (typically, toluene) at SR-RT. According to eqn (2), when a large amount of antisolvent is added to the perovskite precursor solution, *S* will increase, resulting in a high rate of nucleation.

Fig. 2b and c show the LaMer diagrams for the one- and two-step syntheses, respectively, which are composed of three regions, ‘Cs[PbBr₃] aggregate’ accumulation (I), burst nucleation (II) and rapid growth (III), followed by the Ostwald ripening process. In this study, the ‘one-step process’ indicates that the perovskite precursor in polar DMF (1 mL) was injected into 10 mL of the nonpolar antisolvent toluene at RT, resulting in the green-emitting NC synthesis *via* a high degree of supersaturation.

On the other hand, the ‘two-step process’ denotes the sequential mixing of the perovskite precursor solution with the antisolvent. The first stage is the mixing of 5 mL DMF (perovskite precursor) and 5 mL toluene, resulting in the blue-emitting NC synthesis *via* a low degree of supersaturation. However, for collecting these blue emitters, the second stage is usually required. For example, 1 mL of the first stage sample is mixed with 10 mL of antisolvent (Fig. 2c), resulting in a bimodal distribution of NCs, *i.e.*, the blue and green emitters. Note that in Fig. 2c, the solubility of the eventual solvent systems (marginal *vs.* poor) is

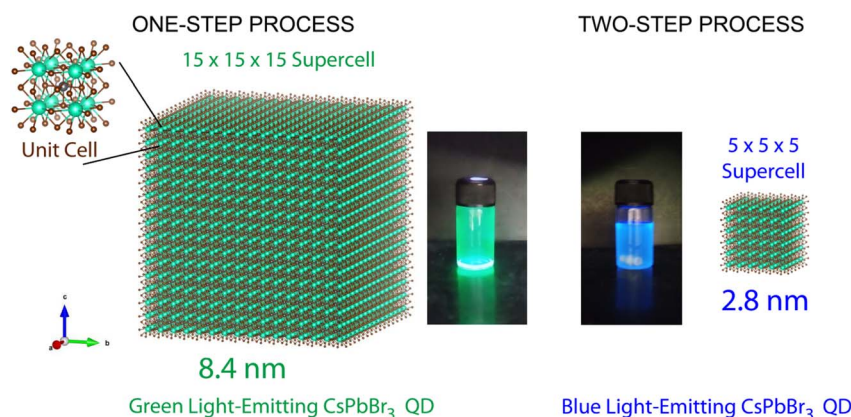


Fig. 1 CsPbBr₃ NCs with a cubic structure: green and blue-emitting NCs depending on the processing conditions: one-step vs. two-step. Unit-cell edge length is 0.587 nm.



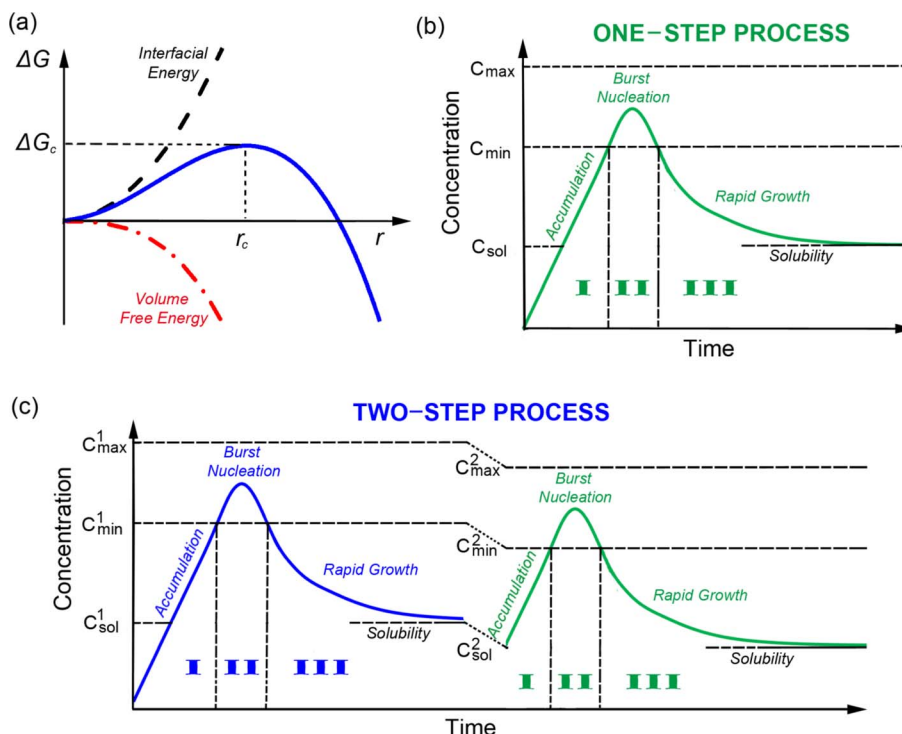


Fig. 2 (a) Free energy change vs. particle size. LaMer diagram: (b) one-step process and (c) two-step process. The regions I, II and III correspond to (monomer) accumulation, burst nucleation and rapid growth, respectively.

different in the first and second stages, affording low and high degrees of supersaturation, respectively. Hence, two different sets of monomer concentrations (C_{\max}^1 , C_{\min}^1 , and C_{sol}^1 for the 1st stage; and C_{\max}^2 , C_{\min}^2 , and C_{sol}^2 for the 2nd stage) should be considered. Here, C_{\max} is the maximum supersaturation concentration, C_{\min} is the minimum supersaturation concentration (*i.e.*, the critical monomer concentration), and C_{sol} is the solubility limit for a given solvent system (hence, the solubility parameter is essential for the SR-RT process). The superscripts 1 and 2 in the concentration (C) symbol denote the first and second stages, respectively. Furthermore, S can be expressed by C/C_{sol} as long as C is larger than C_{sol} .

To understand the miscibility between the polar solvent DMF and the nonpolar antisolvent toluene (Fig. 3a) in the SR-RT process, we employ the Flory–Huggins theory (reduced to the regular solution theory when two solvents are equal in molar volume) as follows,^{38,47,48}

$$\frac{\Delta G_{\text{mix}}}{RT} = \frac{\Delta H_{\text{mix}}}{RT} - \frac{\Delta S_{\text{mix}}}{R} = \frac{\phi_1}{r_1} \ln \phi_1 + \frac{\phi_2}{r_2} \ln \phi_2 + \chi_{12} \phi_1 \phi_2 \quad (3)$$

where ΔG_{mix} is Gibbs free energy of mixing, ΔH_{mix} is the enthalpy of mixing, ΔS_{mix} is the entropy of mixing and χ_{12} is the Flory–Huggins interaction parameter. ϕ_1 and ϕ_2 are the volume fractions of DMF and toluene, whereas $r_1 (=1)$ and r_2 are the relative molar volumes of DMF and toluene, respectively. Note that when r_2 is 1, eqn (1) is reduced to the regular solution theory. However, in this work, the molar volumes of DMF and toluene are $77.4 \text{ cm}^3 \text{ mol}^{-1}$ and $106.3 \text{ cm}^3 \text{ mol}^{-1}$, respectively. Hence, we used eqn (3) with $r_2 = 1.37 = 106.3/77.4$ (=toluene/

DMF, molar volume ratio). Here, the interaction parameter (χ_{12}) between DMF and toluene is defined as

$$\chi_{12} = \frac{\hat{V}_1}{RT} (\delta_1 - \delta_2)^2 \quad (4)$$

where \hat{V}_1 is the molar volume of DMF, whereas δ_1 and δ_2 are the solubility parameters of DMF and toluene, respectively. For example, χ_{12} is 1.34 when \hat{V}_1 is $77.4 \text{ cm}^3 \text{ mol}^{-1}$, $R = 1.987 \text{ cal K}^{-1} \text{ mol}^{-1}$, $T = 298 \text{ K}$, $\delta_1 = 12.1 \text{ cal}^{1/2} \text{ cm}^{-3/2}$ and $\delta_2 = 8.9 \text{ cal}^{1/2} \text{ cm}^{-3/2}$. Accordingly, the enthalpy, entropy and Gibbs free energy of mixing were predicted for the binary DMF–toluene system (Fig. 3). First of all, the poor affinity between DMF and toluene opposes mixing by showing the positive enthalpy of mixing (Fig. 3b). However, because of the entropic gain (Fig. 3c), the Gibbs free energy of mixing decreases when DMF and toluene are mixed together as shown in Fig. 3d. Hence, when the toluene molecules were added to the perovskite precursor solution, they could replace DMF contacting the perovskite precursor molecules, resulting in the burst nucleation and growth of NCs *via* enhanced supersaturation. Note that through the water contact angle (θ_c) data for the CsPbBr_3 (bulk) and CsPbBr_3 NC films, we can estimate their solubility parameters (see the ESI† section for details).^{49,50} For example, when $\theta_c = 10.57^\circ$ for the CsPbBr_3 film,⁵¹ the surface energy was calculated to be 71.594 mJ m^{-2} , resulting in the solubility parameter $\delta_{\text{CsPbBr}_3} = 15.5 \text{ cal}^{1/2} \text{ cm}^{-3/2}$ and $\delta'_{\text{CsPbBr}_3}$ (SI unit) = $31.8 \text{ MPa}^{1/2}$. This estimation is based on the relation, $\delta \propto \sqrt{\gamma}$.^{47,48,52} In the case of CsPbBr_3 NCs complexed with the surface ligands (OA and OAm), $\theta_c = 37.57^\circ$.⁵³ Accordingly, the surface energy (γ) was estimated to be 61.603 mJ m^{-2} , resulting in



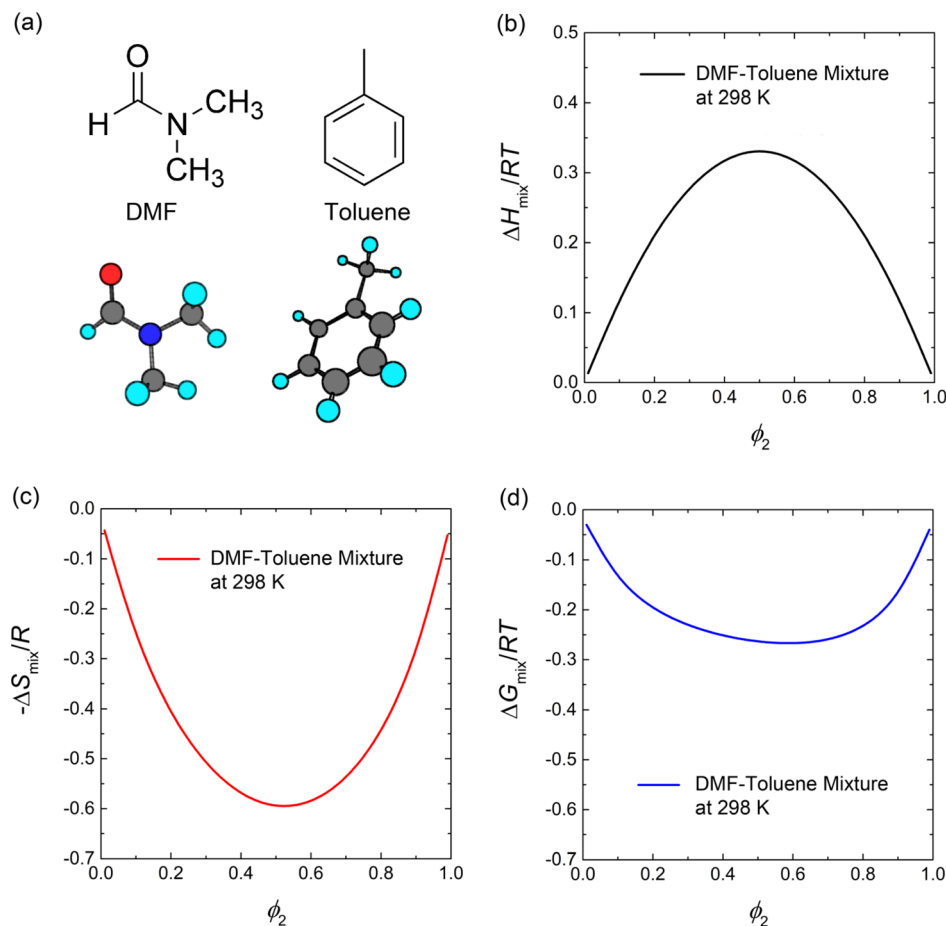


Fig. 3 (a) Chemical structures of DMF and toluene. Prediction of Flory–Huggins theory for (b) enthalpy of mixing, (c) entropy of mixing, and (d) Gibbs free energy of mixing as a function of volume fraction of toluene, ϕ_2 at 298 K.

$\delta_{\text{CsPbBr}_3\text{-NC}} = 14.4 \text{ cal}^{1/2} \text{ cm}^{-3/2}$ and $\delta'_{\text{CsPbBr}_3\text{-NC}} = 29.5 \text{ MPa}^{1/2}$ for the CsPbBr₃ NCs. Hence, the polarity of CsPbBr₃ is partially reduced when complexed with OA and OAm. Note that OA and OAm have the solubility parameters of $7.9 \text{ cal}^{1/2} \text{ cm}^{-3/2}$ and $8.0 \text{ cal}^{1/2} \text{ cm}^{-3/2}$, respectively, exhibiting they are nonpolar, like antisolvent.⁵⁴ However, the CsPbBr₃-surface ligand complex is still polar, allowing the polar DMF to act as a good solvent. In addition, it is notable that DMF is a retrograde solvent,⁵⁵ indicating that the degree of supersaturation will be enhanced with increasing temperature because the solubility of perovskite precursor in DMF

will decrease with increasing temperature. Table 1 shows the summary of the solubility parameters related to this study.^{56,57}

Fig. 4 shows the TEM images of CsPbBr₃ NCs synthesized by one-step (Fig. 4a and b) and two-step (Fig. 4d and e) processes. In the one-step process, the average size of CsPbBr₃ NCs is $\sim 60 \text{ nm}$, which is far from the excitonic confinement regime because its Bohr diameter is $\sim 7 \text{ nm}$. On the other hand, in the two-step process, the CsPbBr₃ NCs exhibit a bimodal distribution (*i.e.*, two separate groups) with average NC sizes of $\sim 13.5 \pm 2.5 \text{ nm}$ (green emitter) and $\sim 3.5 \pm 0.4 \text{ nm}$ (blue emitter),

Table 1 Solubility parameter, molecular weight, density, and molar volume of the solvent, non-solvent, CsPbBr₃ (bulk) and CsPbBr₃ NC complexed with oleic acid and oleylamine. δ' (SI unit) = $\delta \times 2.0455$

Molecule	δ' (MPa ^{1/2})	δ (cal ^{1/2} cm ^{-3/2})	MW (g mol ⁻¹)	ρ (g cm ⁻³)	\hat{V}_i (cm ³ mol ⁻¹)
DMF	24.8	12.1	73.09	0.944	77.4
Toluene	18.2	8.9	92.14	0.867	106.3
Ethyl acetate	18.6	9.1	88.11	0.902	97.7
CsPbBr ₃	31.7	15.5	242	4.57	53.0
CsPbBr ₃ NC	29.5	14.4	242 ^a	4.57 ^a	53.0 ^a

^a Surface ligands are not considered.

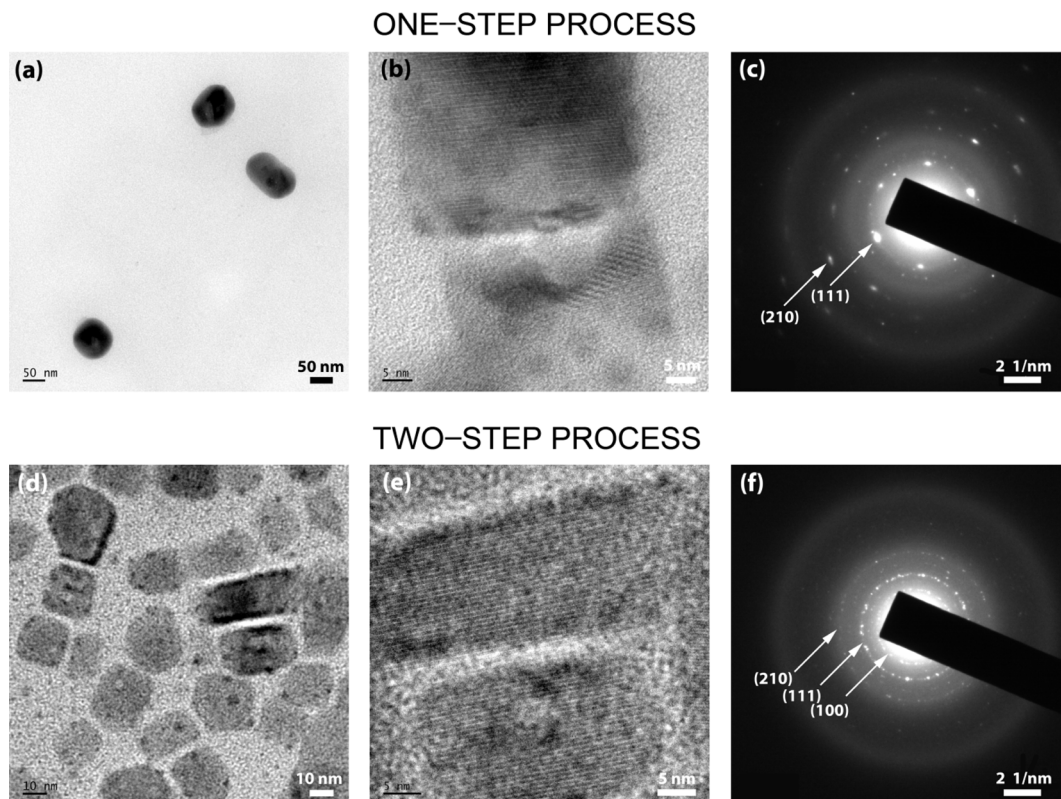


Fig. 4 TEM images of CsPbBr₃NCs synthesized through (a and b) one-step synthesis and (d and e) two-step synthesis. SAED images: (c) one-step synthesis and (f) two-step synthesis.

respectively (Fig. S2†). The selected area electron diffraction (SAED) patterns (Fig. 4c and f) provide additional confirmation of the phases of the NCs. The one-step process displays the SAED pattern of a single crystal-like pattern, whereas the two-step process exhibits a polycrystal pattern because of two different NCs with versatile orientations.

Here, it is worth noting that in the one-step process, there is a high degree of supersaturation (unstable colloidal dispersion) allowing the perovskite precursor components (Cs⁺, Pb²⁺, Br⁻, and its complexes in the presence of OA and OAm) to form Cs [PbBr₃] monomer aggregates resulting in the burst nucleation and fast growth of ~60 nm sized NCs (Fig. 2b). Here, the entropy of mixing between DMF (~1 mL) and toluene (10 mL) is the driving force (Fig. 3c) initiating the aggregate formation of Cs [PbBr₃] monomers because of the repulsive interactions between the polar perovskite precursors and the nonpolar toluene. Interestingly, the phase inversion membrane in polymer science uses the same principle, *i.e.*, the exchange of anti-solvent and solvent molecules for the membrane formation.⁵⁸ On the other hand, in the case of the two-step process, the perovskite precursor molecules can contact the good solvent DMF molecules in the first stage (Fig. 2c) because it is approximately equal mixing between DMF (~5 mL) and toluene (5 mL), resulting in a low degree of supersaturation, *i.e.*, relatively a limited formation of Cs[PbBr₃] monomer aggregates allowing the formation of blue-emitting CsPbBr₃ NCs. It is probably in a metastable state (or weak unstable state) because the larger

green-emitting NCs were not allowed to be formed except for the smaller blue-emitting ones.

At this moment, if we employ the Hildebrand and Hansen solubility parameter,^{37,56,57} the supersaturation phenomena could be quantitatively analyzed during the one-step and two-step processes for the CsPbBr₃ NC synthesis *via* the RT-SR processes. For DMF, $\delta = 12.1 \text{ cal}^{1/2} \text{ cm}^{-3/2}$, whereas for toluene, $\delta = 8.9 \text{ cal}^{1/2} \text{ cm}^{-3/2}$.^{56,57} The polar perovskite precursors ($\delta \sim 14.4\text{--}15.5 \text{ cal}^{1/2} \text{ cm}^{-3/2}$) can aggregate easily in the nonpolar medium (toluene in the one-step process), whereas they can barely aggregate in the DMF-toluene (5 mL : 5 mL mixture) mixture with the average $\delta = (12.1 + 8.9)/2 \approx 10.5 \text{ cal}^{1/2} \text{ cm}^{-3/2}$, *i.e.*, a (partially polar) marginal solvent. Hence, in the first stage of the 'two-step process', the nucleation and dissolution of CsPbBr₃ could reach an unstable equilibrium (Fig. 2a), resulting in the blue-emitting CsPbBr₃ NC formation with an average size of ~3.5 nm. However, to collect these small blue-emitting NCs, some processing solvents, such as nonpolar ethyl acetate and/or toluene, should be used. Resultantly, the colloidal dispersion with the blue-emitting CsPbBr₃ NCs may undergo additional burst nucleation and rapid growth of green-emitting CsPbBr₃ NCs in spite of some depletion of monomers in the first stage, stipulating the purification step for separating the blue-emitters from the green ones.

XRD was employed to characterize the crystal structures of CsPbBr₃ NCs. It has been reported that the tilt of corner-sharing {PbBr₆}⁴⁻ octahedral building blocks causes CsPbBr₃ to exist as



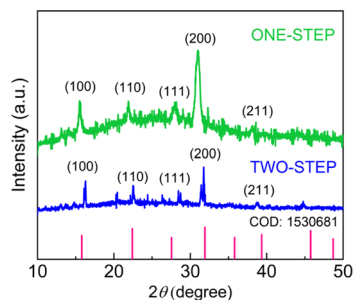


Fig. 5 XRD patterns of CsPbBr₃ NCs synthesized via the one-step and two-step SR method without purification.

polymorphs. The crystal phase symmetry of bulk CsPbBr₃ increases with temperature, undergoing the phase transformation from orthorhombic to tetragonal (*P4mm*) at 88 °C and from tetragonal to cubic (*Pm3m*) at 130 °C.⁴⁷ However, Fig. 5 clearly demonstrates that, due to the well-known high surface energy at the nanoscale, CsPbBr₃ NCs have a cubic phase at RT by displaying the XRD peaks at $2\theta = 16^\circ, 22^\circ, 28^\circ$, and 31° , which correspond to the (100), (110), (111), and (200) crystallographic planes, respectively.⁵⁹ Importantly, in comparison to the one-step process, the two-step process exhibits slightly shifted XRD peaks to a higher degree, revealing a lattice contraction in the nanoscale particles with an edge size of ~ 3.5 – 13.5 nm.²⁴

Fig. 6 shows the UV-Vis absorption and PL emission spectra for (a) one-step and (b) two-step processes before purification, respectively. Fig. 6a shows the absorption peak at 515 nm and the green-light emission peak at 519 nm with a full width at half maximum (FWHM) of ~ 30 nm. Fig. 6b displays the two absorption peaks at 455 nm and ~ 511 nm and the two PL emission peaks at 455 nm and ~ 511 nm (the blue PL from ~ 3.5 nm NCs and the green PL from ~ 14 nm NCs), respectively (see Fig. S2† for NC's size distribution TEM data). The broad band spectrum of the unpurified two-step process samples is due to the wide range distribution of NCs from 2.5 nm to 25 nm, covering both the non-quantum confined (larger than 7 nm) and the quantum-confined (less than 7 nm) regions (see Fig. S2†).

Then, for collecting the blue-emitting CsPbBr₃ NCs, we purified the two-step processed samples (Fig. 4d and e). Fig. 7a shows the UV-Vis absorption and PL emission spectra of the purified blue-emitting NC samples, displaying the absorption peak at 452 nm and the PL emission peak at 457 nm with FWHM of ~ 23 nm. Here, this narrow FWHM data implies the relatively uniform distribution of CsPbBr₃ NCs with a low trap density.^{24,46} Importantly, through the Tauc plot equation, $(\alpha h\nu)^n = B(h\nu - E_g)$, we can quantify the optical bandgap (E_g) of the NC samples (Fig. 7b). Here, $h\nu$ is the photon energy, α is the absorption coefficient, B is a constant relative to the material, and n is either 2 for a direct transition or 0.5 for an indirect transition.⁶⁰ As shown in Fig. 7b, the one-step and two-step

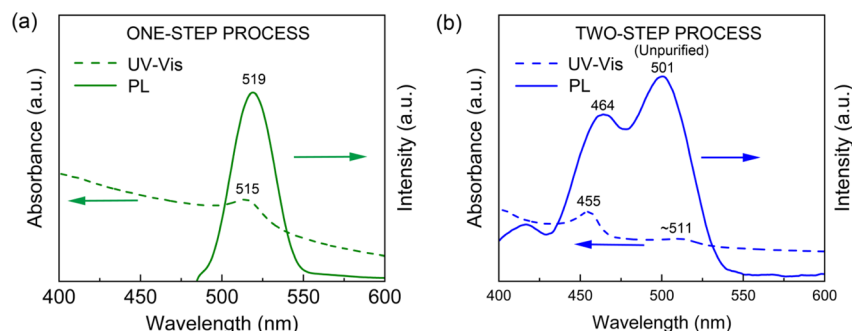


Fig. 6 UV-vis and PL spectra of CsPbBr₃ NCs: (a) one-step process and (b) two-step process without purification.

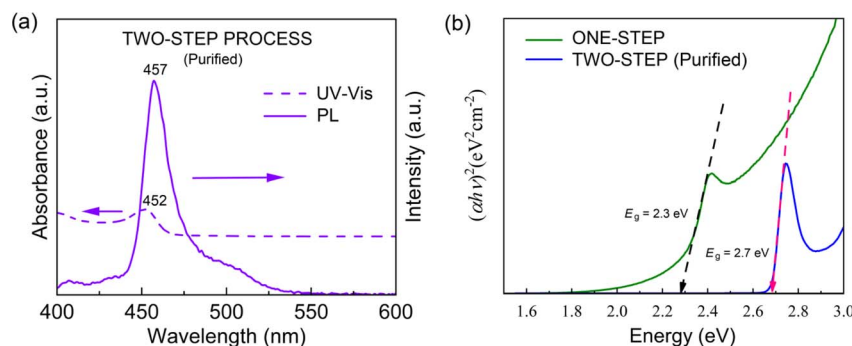


Fig. 7 (a) UV-vis and PL spectra for the purified two-step synthesized CsPbBr₃ NCs. (b) Tauc plot of one-step CsPbBr₃ NCs and two-step CsPbBr₃ NCs after purification.



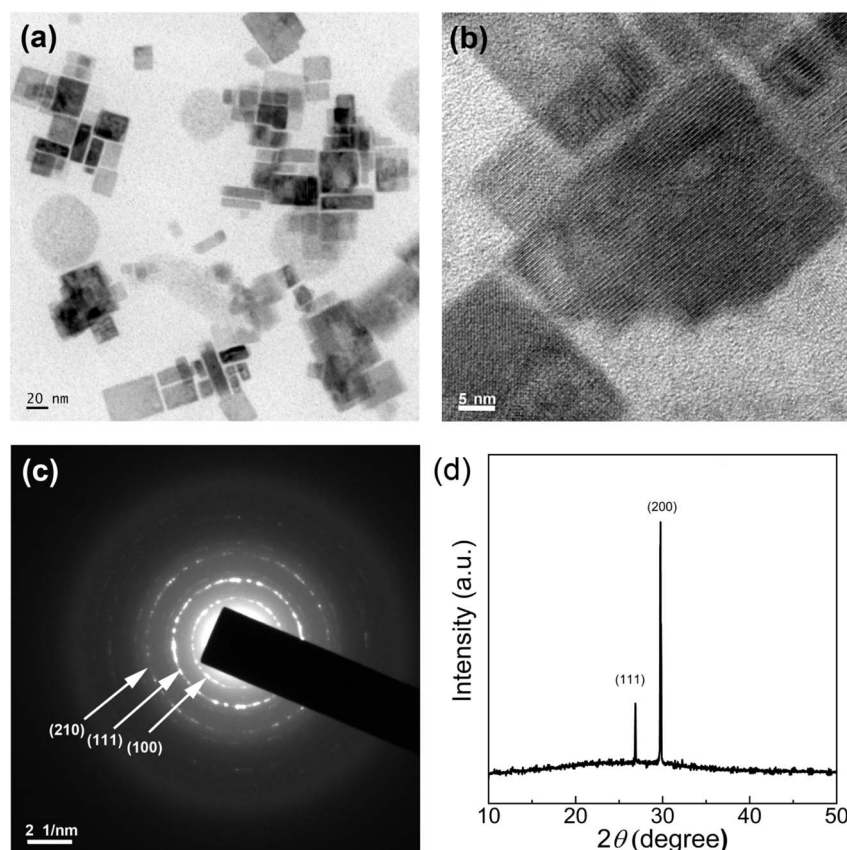
TWO-STEP PROCESS ($\text{CuBr}_2 : \text{PbBr}_2 = 1:4$)

Fig. 8 TEM images of CsPbBr_3 NCs synthesized through the two-step process with $\text{CuBr}_2 : \text{PbBr}_2 = 1 : 4$ mole ratio: (a) scale bar = 20 nm, (b) scale bar = 5 nm, and (c) SAED image. (d) XRD pattern of CsPbBr_3 NCs synthesized via a two-step process with $\text{CuBr}_2 : \text{PbBr}_2 = 1 : 4$ mole ratio.

processed samples exhibit an optical bandgap of 2.3 eV (green emitter) and 2.7 eV (blue one), respectively, demonstrating the process-nanostructure-optical property relationship.

We expanded the aforementioned two-step process by incorporating CuBr_2 as an additive into the perovskite precursor solutions with $\text{CuBr}_2 : \text{PbBr}_2 = 1 : 4$ (molar ratio) for the first time *via* SR at RT. Here, by adding Cu^{2+} cations as well as Br^- anions with high Gutmann's donor number ($D_N = 33.7$, Lewis basicity),⁶¹ we may modify the interactions between perovskite precursor-solvent (DMF with $D_N = 26.6$; toluene with $D_N = 0.1$), affecting the crystallization process of LHPs.^{50,61–63} Fig. 8a and b show the HR-TEM images of CsPbBr_3 NCs processed with the CuBr_2 additive, displaying the clear cubic NCs, indicating that the additive may stabilize the nanoscale cube with a sharp vertex in spite of its increased surface energy (compared to the spherical structure). Here, we observed again a bimodal distribution, composed of average $\sim 3.8 \pm 0.7$ nm and $\sim 21.4 \pm 9.5$ nm sized NCs (Fig. S3†). Note that this NC size is slightly larger than that of NCs without the additive in Fig. 4 and S2.† Furthermore, Fig. 8c shows the corresponding SAED image, indicating that the cubic CsPbBr_3 NCs are oriented to the $[110]$ direction on top of the TEM copper grid. On the other hand, the XRD pattern of the cubic CsPbBr_3 NCs (Fig. 8d) displays two strong peaks at

26.8° and 29.9° , corresponding to (111) and (200) crystallographic planes, indicating that the cubic NCs are oriented more to the $[200]$ direction on top of the glass slide. Hence, compared to the XRD in Fig. 5, the XRD pattern in Fig. 8d is much more simplified, indicating the enhanced orientational order when processed with the CuBr_2 additive.

Fig. 9 shows the UV-Vis absorption and PL emission spectra for (a) the unpurified and (b) purified CsPbBr_3 NCs with CuBr_2 . Compared to the unpurified sample in Fig. 6b (without CuBr_2), the unpurified sample in Fig. 9a (with CuBr_2) shows a slight red-shift (UV-Vis absorption peaks from '455 nm and 511 nm' to '566 nm and 521 nm' whereas PL emission peaks from '464 nm and 501 nm' to '466 nm and 501 nm') (compare Fig. 6b and 9a). The same trend was also observed in the purified samples by displaying the minor red shift (UV-Vis absorption from 452 nm to 458 nm whereas PL emission from 457 nm to 460 nm). This red shift could be rationally understood by observing the partial increase of the CsPbBr_3 NC size in the presence of the CuBr_2 additive, as shown in Fig. S1 and S6.† Furthermore, it is interesting to observe the reduced PL FWHM of ~ 18.5 nm (Fig. 9b), which is significantly smaller than ~ 23 nm in Fig. 7 (without CuBr_2), indicating that the size-focusing effect is available when processed with the CuBr_2 additive. However, because of the



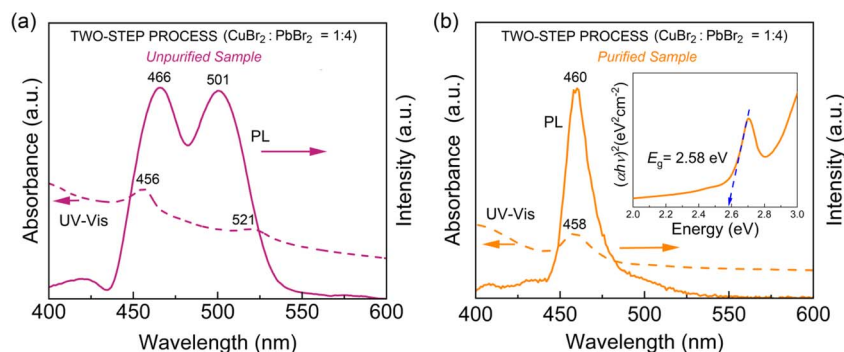


Fig. 9 UV-vis and PL spectra of CsPbBr₃ NCs synthesized through two-step synthesis with doping (CuBr₂ : PbBr₂ = 1 : 4 mole ratio): (a) unpurified sample and (b) purified sample. Inset: Tauc plot of the purified sample.

partial increase of NC size, the optical bandgap is accordingly reduced from 2.7 eV (Fig. 7b) to \sim 2.6 eV (see the inset in Fig. 9b), displaying the quantum size effect.

The two-step process produces a bimodal distribution, as demonstrated through the TEM data in Fig. 4d, S2, 8a, and S3.[†] Hence, it would be valuable to examine the stability and crystallization of the original solution samples after the first stage 'separately' in the two-step process. For this purpose, after the initial mixing of 'the precursor solution in 5 mL DMF' and '5 mL toluene', the solution was stored for aging effect at RT – this is a low degree of supersaturation state. Fig. 10 shows the UV-Vis absorption and PL emission spectra as a function of aging time at RT. Fig. 10a displays clearly that the absorption increases with time. However, based on the peak's location, we determined that there is only the blue-emitting CsPbBr₃ NCs without

the Oswald ripening effect related to the green emitter growth (the quenching mechanism is simply all monomer consumption at RT). Furthermore, when the UV-Vis absorption data was plotted at the wavelength (λ) of 410 nm with aging time, a saturation behavior was observed after \sim 50–100 hours (Fig. 10b). Subsequently, we examined the PL emission behavior as a function of aging time. As shown in Fig. 10b, the PL increases initially but decreases after 24 hours, indicating NCs might be deactivated, *i.e.*, quenching the PL emission. Furthermore, the PL red-shift was observed, indicating a partial growth of blue-emitting CsPbBr₃ NCs, but still, it is a blue emitter, indicating that there might be a balance between formation and dissolution of the blue-emitting NCs in this low degree of supersaturated state. However, recall that for collecting these NCs, additional nonpolar antisolvent should be

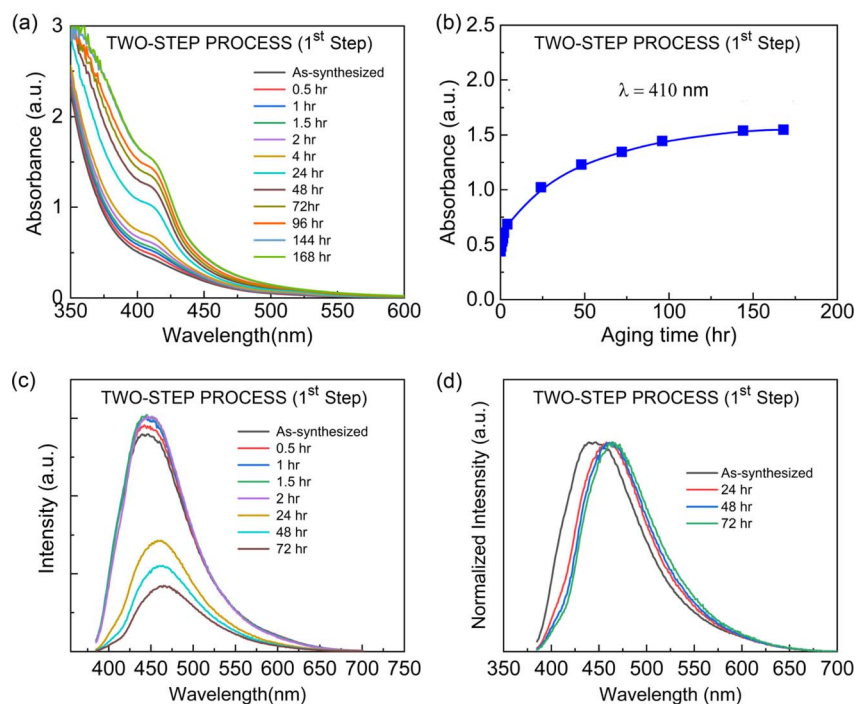


Fig. 10 Aging effect on the optical properties of CsPbBr₃ NCs (after the first step in the 'two-step process') at room temperature. (a) UV-vis absorption spectra as a function of aging time at room temperature. (b) The absorption at $\lambda = 410$ nm. (c) PL emission spectra as a function of aging time at room temperature. (d) Normalized PL intensity as a function of aging time at room temperature.



SUPERSATURATED RECRYSTALLIZATION AT ROOM TEMPERATURE

Solubility Parameter-Based Nanocrystal Size Control Model

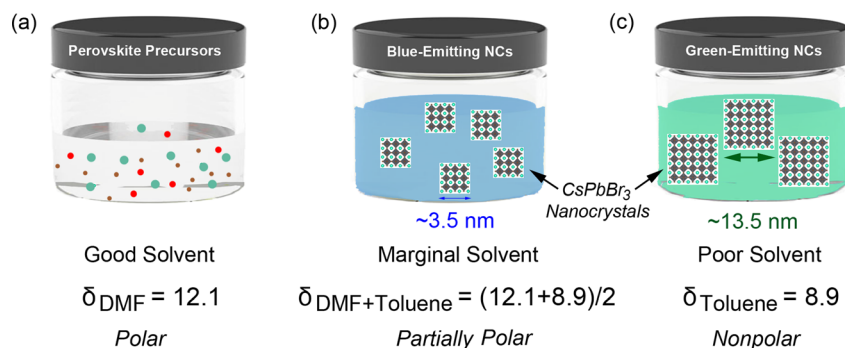


Fig. 11 Supersaturated recrystallization at room temperature: solubility parameter-based nanocrystal size control model: (a) good solvent = polar, (b) marginal solvent = partially polar, and (c) poor solvent or antisolvent = nonpolar.

required as a processing solvent, resulting in another nucleation and growth of green emitters from the new monomer aggregates generated by the enhanced degree of supersaturation (Fig. 2c). Moreover, in the two-step process (1st step), the UV-Vis and PL spectra display that the CsPbBr₃ NCs grow with a wide range of size distribution (Fig. 10). However, still, the majority of the NCs are in a quantum-confined regime. However, when the antisolvent toluene is additionally added for the second time, it may cause some of the NCs to aggregate and grow, resulting in non-quantum confined NCs. Hence, two competing peaks were observed in Fig. 6b.

Fig. 11 is the summary of this work suggesting 'the solubility parameter-based nanocrystal size control model' for explaining the SR process at RT. When the perovskite precursors are in a good solvent like DMF, there is no nucleation and growth of NCs because they can stay as a well-dispersed colloidal system. However, by adding an antisolvent (toluene) into the perovskite precursor solution in DMF with a $\sim 50:50$ volume ratio, the liquid medium becomes a marginal solvent with partial polarity, resulting in the burst nucleation and rapid growth of blue-emitting CsPbBr₃ NCs. Here, the DMF-toluene $50:50$ mixture provides a significant solubility for colloidal perovskite precursors (Fig. 2c), and no sufficient monomer aggregates remain for further growing to green emitters at this low supersaturation level. Finally, if the liquid medium is dominantly nonpolar (toluene \gg DMF), the green-emitting NCs can be easily grown in the presence of blue-emitting NCs. Hence, the solubility parameters (or solubility) of the solvent and solvent-antisolvent mixture can serve as a key factor for the nanoscale size regulation in the SR process at RT, affecting (1) the nucleation and growth of NCs and (2) the balance between formation and dissolution of Cs[PbBr₃] monomers and NCs in line with the LaMer diagram in Fig. 2 and 11.

4. Conclusions

The nucleation and growth of CsPbBr₃ NCs were studied in view of the classical LaMer model when the supersaturated recrystallization was carried out at room temperature. For this

purpose, we compared one-step and two-step processes to elucidate the formation mechanism of NCs. Resultantly, when the nonpolar toluene (antisolvent) was much larger in volume than the polar DMF (solvent), the $\sim 60 \text{ nm}$ sized green-emitting NCs were synthesized *via* the one-step process under a high degree of supersaturation. On the other hand, when the antisolvent volume is comparable to that of the solvent, the $\sim 3.5 \text{ nm}$ -sized blue-emitting NCs were synthesized *via* a two-step process using a low degree of supersaturation. In this study, by employing the Hildebrand and Hansen solubility parameter concept, we quantitatively explained the solvent quality (good, marginal, and poor). Hence, we named this approach 'the solubility parameter-based nanocrystal size control model' because supersaturation is a function of 'solubility and polarity' (expressed as solubility parameter) and 'antisolvent-solvent volume ratio' (considered as average solubility parameter). Furthermore, based on the Flory-Huggins model, we predicted that the antisolvent-solvent mixing is driven by the entropy of mixing, allowing the crystallization of the perovskite precursor to aggregate *via* SR operating at RT. Finally, in the presence of the CuBr₂ additive in the two-step process, we observed a partial red-shift in both absorption and emission spectra from the quantum size effect (a slight increase of nanocube). In addition, the PL emission spectra showed a reduced PL FWHM of $\sim 18.5 \text{ nm}$ (reduced size scattering and enhanced size focusing) from the $\sim 3.8 \text{ nm}$ NCs. Finally, we believe that our finding, *i.e.*, the importance of the solubility parameter as an NC size control factor for the SR method at RT, will contribute to further advancing the perovskite nanocrystal technology and beyond. Future work may include the formation mechanism of NCs *via* SR-RT as a function of the average solubility parameter from the versatile antisolvent-solvent mixtures.

Author contributions

Writing – original draft preparation, D. A. I.; experiments and formal analysis, D. A. I., M. A., D. M., J. K. P., L. T., A. T., S. T. and J. Y. K.; and writing – review and editing, J. Y. K.



Conflicts of interest

The authors declare no competing financial interest.

Acknowledgements

This research received no external funding. The financial support from the Jimma Institute of Technology and Mizan-Tepi University in Ethiopia is appreciated by D. A. I.

References

- 1 F. P. G. de Arquer, D. V. Talapin, V. I. Klimov, Y. Arakawa, M. Bayer and E. H. Sargent, *Science*, 2021, **373**, eaaz8541.
- 2 Y. Pan, Y. Zhang, W. Kang, N. Deng, Z. Yan, W. Sun, X. Kang and J. Ni, *Mater. Adv.*, 2022, **3**, 4053–4068.
- 3 G. Abiram, M. Thanishaichelvan, P. Ravirajan and D. Velauthapillai, *Nanomaterials*, 2022, **12**, 2396.
- 4 C. Huangfu and L. Feng, *Sens. Actuators, B*, 2021, **344**, 130193.
- 5 D. Jia, M. Xu, S. Mu, W. Ren and C. Liu, *Biosensors*, 2022, **12**, 754.
- 6 C. Zhu, M. Marczak, L. Feld, S. C. Boehme, C. Bernasconi, A. Moskalenko, I. Cherniukh, D. Dirin, M. I. Bodnarchuk, M. V. Kovalenko and G. Rainò, *Nano Lett.*, 2022, **22**, 3751–3760.
- 7 X. Zhang, Y. Zhou, L. Peng, Z. Lin, Y. Chang, Z. Zhou and Y. Li, *ACS Appl. Nano Mater.*, 2022, **5**, 17012–17021.
- 8 Y. Y. Zhao, Y. F. Liu, Y. G. Bi, C. H. Li, Y. F. Wang, H. W. Li, Q. W. Zhang, C. Lv and Y. Q. Wu, *Org. Electron.*, 2023, **116**, 106775.
- 9 F. Zeng, Y. Tan, W. Hu, X. Tang, X. Zhang and H. Yin, *J. Lumin.*, 2022, **245**, 118788.
- 10 L. Protesescu, S. Yakunin, M. I. Bodnarchuk, F. Krieg, R. Caputo, C. H. Hendon, R. X. Yang, A. Walsh and M. V. Kovalenko, *Nano Lett.*, 2015, **15**, 3692–3696.
- 11 F. Ye, H. Zhang, P. Wang, J. Cai, L. Wang, D. Liu and T. Wang, *Chem. Mater.*, 2020, **32**, 3211–3218.
- 12 S. M. H. Qaid, H. M. Ghaithan, B. A. Al-Asbahi and A. S. Aldwayyan, *J. Phys. Chem. C*, 2021, **125**, 9441–9452.
- 13 P. Ding, P. K. Ko, P. Geng, D. Chen, Z. Xing, H. L. T. Tsang, K. S. Wong, L. Guo and J. E. Halpert, *Adv. Opt. Mater.*, 2024, **12**, 2302477.
- 14 S. Peng, S. Wang, D. Zhao, X. Li, C. Liang, J. Xia, T. Zhang, G. Xing and Z. Tang, *Small Methods*, 2019, **3**, 1900196.
- 15 J. Leng, T. Wang, X. Zhao, E. W. Y. Ong, B. Zhu, J. D. A. Ng, Y. C. Wong, K. H. Khoo, K. Tamada and Z. K. Tan, *J. Phys. Chem. Lett.*, 2020, **11**, 2036–2043.
- 16 L. Peng, A. Dutta, R. Xie, W. Yang and N. Pradhan, *ACS Energy Lett.*, 2018, **3**, 2014–2020.
- 17 T. Udayabhaskararao, M. Kazes, L. Houben, H. Lin and D. Oron, *Chem. Mater.*, 2017, **29**, 1302–1308.
- 18 Y. Dong, T. Qiao, D. Kim, D. Parobek, D. Rossi and D. H. Son, *Nano Lett.*, 2018, **18**, 3716–3722.
- 19 H. Huang, A. S. Susha, S. V. Kershaw, T. F. Hung and A. L. Rogach, *Adv. Sci.*, 2015, **2**, 1500194.
- 20 X. Li, Y. Wu, S. Zhang, B. Cai, Y. Gu, J. Song and H. Zeng, *Adv. Funct. Mater.*, 2016, **26**, 2435–2445.
- 21 G. Almeida, L. Goldoni, Q. Akkerman, Z. Dang, A. H. Khan, S. Marras, I. Moreels and L. Manna, *ACS Nano*, 2018, **12**, 1704–1711.
- 22 A. Dutta, S. K. Dutta, S. Das Adhikari and N. Pradhan, *ACS Energy Lett.*, 2018, **3**, 329–334.
- 23 X. Zhang, X. Bai, H. Wu, X. Zhang, C. Sun, Y. Zhang, W. Zhang, W. Zheng, W. W. Yu and A. L. Rogach, *Angew. Chem., Int. Ed.*, 2018, **57**, 3337–3342.
- 24 J. Cao, C. Yan, C. Luo, W. Li, X. Zeng, Z. Xu, X. Fu, Q. Wang, X. Chu, H. Huang, X. Zhao, J. Lu and W. Yang, *Adv. Opt. Mater.*, 2021, **9**, 2100300.
- 25 C. Bi, S. Wang, Q. Li, S. V. Kershaw, J. Tian and A. L. Rogach, *J. Phys. Chem. Lett.*, 2019, **10**, 943–952.
- 26 G. Pan, X. Bai, W. Xu, X. Chen, Y. Zhai, J. Zhu, H. Shao, N. Ding, L. Xu, B. Dong, Y. Mao and H. Song, *ACS Appl. Mater. Interfaces*, 2020, **12**, 14195–14202.
- 27 W. Van der Stam, J. J. Geuchies, T. Altantzis, K. H. W. Van Den Bos, J. D. Meeldijk, S. Van Aert, S. Bals, D. Vanmaekelbergh and C. De Mello Donega, *J. Am. Chem. Soc.*, 2017, **139**, 4087–4097.
- 28 M. Liu, G. Zhong, Y. Yin, J. Miao, K. Li, C. Wang, X. Xu, C. Shen and H. Meng, *Adv. Sci.*, 2017, **4**, 1700335.
- 29 C. Sun, Y. Jiang, L. Zhang, K. Wei and M. Yuan, *ACS Nano*, 2023, **17**, 17600–17609.
- 30 M. Jung, S.-G. Ji, G. Kim and S. I. Seok, *Chem. Soc. Rev.*, 2019, **48**, 2011–2038.
- 31 S. G. Kwon and T. Hyeon, *Small*, 2011, **7**, 2685–2702.
- 32 J. Park, J. Joo, S. G. Kwon, Y. Jang and T. Hyeon, *Angew. Chem., Int. Ed.*, 2007, **46**, 4630–4660.
- 33 V. K. LaMer and R. H. Dinegar, *J. Am. Chem. Soc.*, 1950, **72**, 4847–4854.
- 34 V. K. LaMer, *Ind. Eng. Chem.*, 1952, **44**, 1270–1277.
- 35 C. d. M. Donegá, P. Liljeroth and D. Vanmaekelbergh, *Small*, 2005, **1**, 1152–1162.
- 36 B. Shu, Y. Chang, E. Xu, S. Yang and J. Zhang, *Nanotechnology*, 2021, **32**, 145712.
- 37 C. M. Hansen, *Prog. Org. Coat.*, 2004, **51**, 77–84.
- 38 P. J. Flory, *J. Chem. Phys.*, 1942, **10**, 51–61.
- 39 M. L. Huggins, *J. Phys. Chem.*, 1942, **46**, 151–158.
- 40 P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, A. Dal Corso, S. De Gironcoli, S. Fabris, G. Fratesi, R. Gebauer, U. Gerstmann, C. Gougoussis, A. Kokalj, M. Lazzeri, L. Martin-Samos, N. Marzari, F. Mauri, R. Mazzarello, S. Paolini, A. Pasquarello, L. Paulatto, C. Sbraccia, S. Scandolo, G. Sclauzero, A. P. Seitsonen, A. Smogunov, P. Umari and R. M. Wentzcovitch, *J. Phys.: Condens. Matter*, 2009, **21**, 395502.
- 41 I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, J. P. Perdew, A. Ruzsinszky, X. Zhou and K. Burke, *Phys. Rev. Lett.*, 2008, **100**, 136406.
- 42 H. M. Ghaithan, Z. A. Alahmed, S. M. H. Qaid, M. Hezam and A. S. Aldwayyan, *ACS Omega*, 2020, **5**, 7468–7480.
- 43 H. Haug and W. K. Stephan, *Quantum Theory of Optical and Electronic Properties of Semiconductors*, World Scientific Publishing Company, Tuck Link, Singapore, 4th edn, 2004.



- 44 D. Norris and M. Bawendi, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1996, **53**, 16338–16346.
- 45 J. Butkus, P. Vashishtha, K. Chen, J. K. Gallaher, S. K. K. Prasad, D. Z. Metin, G. Laufersky, N. Gaston, J. E. Halpert and J. M. Hodgkiss, *Chem. Mater.*, 2017, **29**, 3644–3652.
- 46 C. Bi, Z. Yao, X. Sun, X. Wei, J. Wang and J. Tian, *Adv. Mater.*, 2021, **33**, 2006722.
- 47 J. Y. Kim, *Macromolecules*, 2019, **52**, 4317–4328.
- 48 J. Y. Kim, *Macromolecules*, 2018, **51**, 9026–9034.
- 49 A. T. Gidey, E. Assayehegn and J. Y. Kim, *ACS Appl. Energy Mater.*, 2021, **4**, 6923–6932.
- 50 J. Y. Kim, Y. Yoo, J. Kim, H. J. Park, W. Cho, S. Lee, Y.-E. Sung and S. Bae, *ACS Appl. Opt. Mater.*, 2024, **2**, 108–117.
- 51 X. Zeng, W. Li, C. Yan, J. Cao, X. Fu and W. Yang, *J. Mater. Chem. C*, 2021, **9**, 15967–15976.
- 52 S. Nilsson, A. Bernasik, A. Budkowski and E. Moons, *Macromolecules*, 2007, **40**, 8291–8301.
- 53 A. Gao, J. Yan, Z. Wang, P. Liu, D. Wu, X. Tang, F. Fang, S. Ding, X. Li, J. Sun, M. Cao, L. Wang, L. Li, K. Wang and X. W. Sun, *Nanoscale*, 2020, **12**, 2569–2577.
- 54 G. Welyab, M. Abebe, D. Mani, J. K. Paduvilan, L. Thottathi, A. Thankappan, S. Thomas, T. H. Wondimu and J. Y. Kim, *Next Nanotechnology*, 2024, **5**, 100053.
- 55 M. Saidaminov, A. L. Abdelhaby, G. Maculan and O. M. Bakr, *Chem. Commun.*, 2015, **51**, 17658–17661.
- 56 C. M. Hansen, *Hansen Solubility Parameters – A User's Handbook*, CRC Press, Boca Raton, FL, 2000.
- 57 M. Belmares, M. Blanco, W. A. Goddard III, R. B. Ross, G. Caldwell, S.-H. Chou, J. Pham, P. M. Olofson and C. Thomas, *J. Comput. Chem.*, 2004, **25**, 1814.
- 58 P. van de Witte, P. J. Dijkstra, J. W. A. van den Berg and J. Feijen, *J. Membr. Sci.*, 1996, **117**, 1–31.
- 59 S. Hirotsu, J. Harada, M. Iizumi and K. Gesi, *J. Phys. Soc. Jpn.*, 1974, **37**, 1393–1398.
- 60 Y. Yin, W. Luan, C. Zhang and F. Yang, *IOP Conf. Ser. Earth Environ. Sci.*, 2017, **100**, 012057.
- 61 V. Gutmann, *Coord. Chem. Rev.*, 1976, **18**, 225–255.
- 62 A. A. Petrov, A. A. Ordinartsev, S. A. Fateev, E. A. Goodilin and A. B. Tarasov, *Molecules*, 2021, **26**, 7541.
- 63 A. T. Gidey and J. Y. Kim, *J. Mater. Sci.: Mater. Electron.*, 2020, **31**, 12257–12268.

