

Chemical Science

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: P. K. Maitra, V. A. Rinshad, N. Hickey and P. S. Mukherjee, *Chem. Sci.*, 2026, DOI: 10.1039/D5SC08202A.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

ARTICLE

Selective photocatalytic oxidative cleavage of terminal alkynes to carboxylic acids within a water-soluble Pd₆ nanocage

Pranay Kumar Maitra,^a Valiyakath Abdul Rinshad,^a Neal Hickey,^b Partha Sarathi Mukherjee^{a*}

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

The selective oxidative cleavage of terminal alkynes to carboxylic acids under mild, environmentally benign conditions remains a major challenge in catalysis due to diverse reaction profile of the terminal alkynes. Herein, we report a cavity-mediated UV light-driven oxidation of terminal alkynes to the corresponding carboxylic acids in aqueous medium using a water-soluble Pd₆ nanocage. This transformation proceeds without the need for ozonolysis or precious metal oxide catalysts. Mechanistic investigations indicates that generation of hydroxyl radicals mediates the oxidative cleavage of terminal alkynes. Notably, we achieved a chemo-selective transformation of arylalkynes bearing methyl substituents, which are typically susceptible to undergo oxidation under confinement. Furthermore, the recyclability of the cage in the catalysis was demonstrated over multiple cycles with the retention of catalytic activity. This work highlights the potential of selective photo-induced oxidative transformations of substrates using coordination cages in aqueous medium.

Introduction

Nature employs confined nano-spaces to mediate organic transformations by precisely controlling the reaction environment. In such catalytic processes, non-covalent interactions such as hydrogen bonding, π - π interactions, and van der Waals forces play a vital role in governing both the rate and selectivity of the reactions.¹ Inspired by these natural processes, researchers have designed synthetic systems that attempt to replicate such confinement effects.² Examples include extended porous materials like metal-organic frameworks (MOFs) and covalent organic frameworks (COFs),³ as well as discrete molecular architectures such as organic cages, capsules, macrocycles⁴ and coordination cages.⁵ Among these systems, coordination cages formed via coordination-driven self-assembly are particularly attractive due to their structural precision, solubility, and customizable internal cavities.⁶ These hydrophobic cavities are capable of selectively hosting guest molecules and have been applied in various domains including molecular recognition,⁷ chemical sensing,⁸ stabilization of reactive intermediates,⁹ selective separations,¹⁰ and light energy capture.¹¹ Additionally, metal-organic cages have been well explored as nano-vessels for carrying out a wide variety of organic transformations, including Diels-Alder cycloadditions,¹² Knoevenagel condensations,¹³ and oxidative reactions.¹⁴

Motivated by the advances in confinement mediated catalysis, there is a growing interest in developing green and recyclable supramolecular catalytic systems for oxidative transformations in aqueous medium.¹⁵ In particular, the oxidative cleavage of terminal alkynes to yield carboxylic acids is a synthetically valuable reaction which provides key intermediates in pharmaceuticals, agrochemicals, and polymer synthesis.¹⁶ Generally, the synthesis of carboxylic acids from alkynes involves either ozonolysis or two-step dihydroxylation and oxidative cleavage of diols with sodium periodate. Similarly, the direct conversion of alkyne to carboxylic acid can be achieved using osmium, manganese, rhodium, iridium, and other metals or metal oxides under harsh/inert conditions which limit its practical applications and sustainability.¹⁷ Recent research efforts have shifted towards exploring milder, oxygen-based oxidative strategies; however, the development of efficient and reusable catalytic systems for direct terminal alkyne oxidative cleavage under mild and aqueous conditions remains a significant challenge. Coordination cages, with their modularity, water solubility, and ability to stabilize reactive intermediates through non-covalent interactions, represent a promising platform to address this gap in oxidative catalysis.

Herein, we describe a highly efficient and selective oxidative cleavage of terminal alkynes to the corresponding carboxylic acids using a water-soluble Pd(II) coordination cage (**C**₁) under mild reaction conditions. The Pd₆ nanocage **C**₁ was constructed via coordination-driven self-assembly of a C₃-symmetric benzene-triimidazole ligand (**L**) with 90° *cis*-(1*R*, 2*R*-dch)Pd(NO₃)₂ acceptor unit (**M**) (1*R*, 2*R*-dch) = *trans*-1*R*, 2*R*-cyclohexane-1,2-diamine, resulting predominantly in a well-defined unexpected distorted octahedral structure (**C**₁) as the major product (Scheme 1) instead of the


^aDepartment of Inorganic and Physical Chemistry, Indian Institute of Science, Bangalore- 560012, India. Email: psm@iisc.ac.in

^bDepartment of Chemical and Pharmaceutical Sciences, University of Trieste, Trieste 34127, Italy

*Electronic Supplementary Information (ESI) available: NMR Spectra, ESI-MS, CIF file, optimized structures, experimental details (PDF). See DOI: 10.1039/x0xx00000x.



expected double-square architecture (**C**₃) that was formed using the N,N,N',N'-tetramethylethylene-1,2-diamine cis-blocked Pd(II)-acceptor.^{13a} In addition to the octahedral cage **C**₁, the double-square cage (**C**₂) was also observed to form in minor amount (~8%) in the self-assembly reaction. The unusual octahedral structure of the cage **C**₁ was unambiguously confirmed by single-crystal X-ray diffraction (SCXRD), which revealed the presence of a hydrophobic internal cavity. Host-guest binding studies demonstrated that **C**₁ can effectively encapsulate a range of terminal alkynes, driven by hydrophobic and π - π interactions within the confined interior. Under UV irradiation this cage mediates the oxidative cleavage of ethynylbenzene to benzoic acid in high yield (Scheme 1). Moreover, we achieved a chemo-selective transformation of alkyne to corresponding carboxylic acid in the presence of alkyl group. Such a selective oxidation of only the alkyne group without affecting the alkyl group is noteworthy as alkyl substituent in aromatic ring are known to undergo oxidation in the presence of air under confinement.^{15f} This transformation proceeds without the need for harsh oxidants, which showcases the potential of coordination cages as recyclable nanoreactors for environmentally benign oxidative transformations.

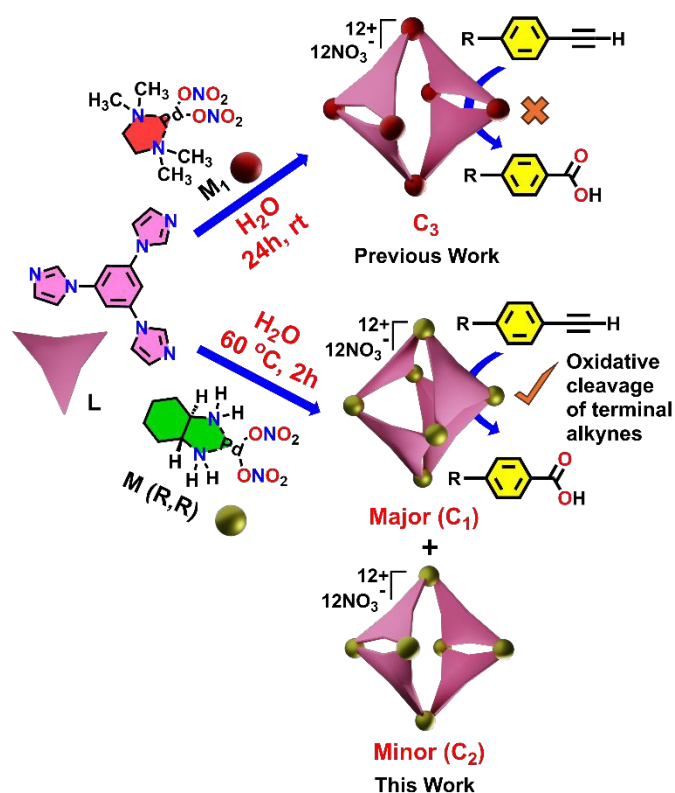

Scheme 1. Schematic representation of the synthesis of cage **C**₁ and its use in catalysing terminal alkyne oxidation.

Results and Discussion

The tridentate ligand **L** was prepared according to a previously described method.^{13a} Self-assembly of **L** with 90° cis-blocked Pd(II) acceptor (**M**) in a 2:3 molar ratio in water at 70 °C for 12 hours

resulted in a clear, colourless solution. The ¹H NMR spectrum of the product displayed three sharp signals in the aromatic region, closely resembling those of the free ligand **L**, which indicates the formation of a highly symmetric coordination cage (**C**₁) (Figure 1a, b).

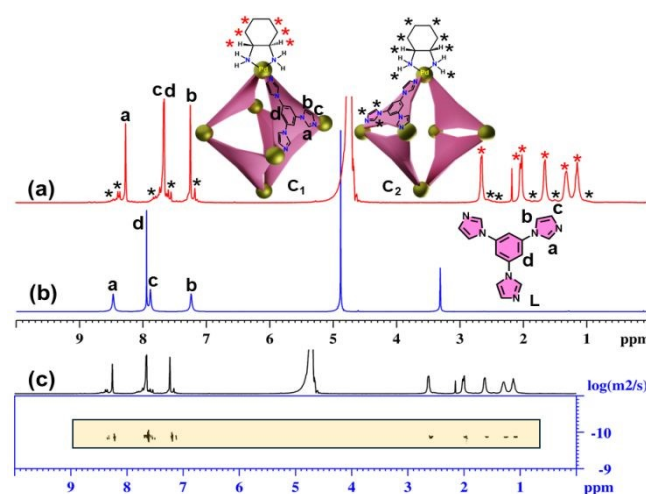


Figure 1. ¹H NMR spectra of (a) self-assembled product (NO_3^- analogue in D_2O , 298 K), (b) **L** (CD_3OD , 298 K), (c) ¹H-DOSY NMR of the self-assembled product (D_2O , 298 K).

In addition to the major signals, a set of minor peaks with two-fold splitting of the original signals was also observed, suggesting the formation of a minor self-assembled product (**C**₂) with lower symmetry. A DOSY NMR spectrum of self-assembled product/s showed a single, well-defined diffusion coefficient for both the major and minor species, indicating that they are similar in size (Figure 1c).

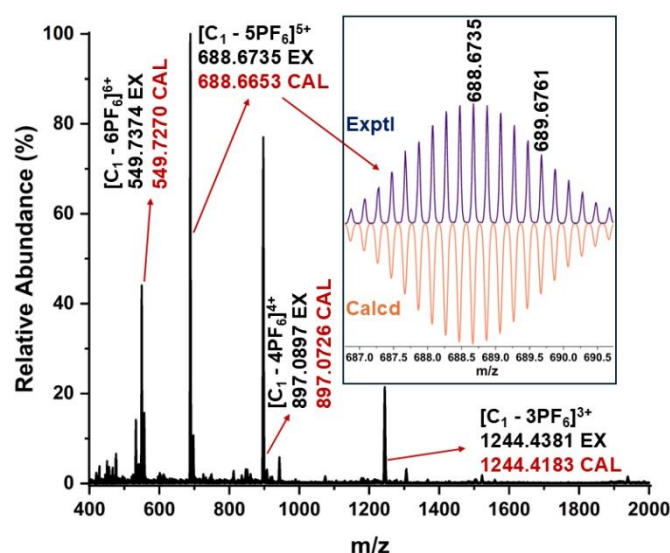


Figure 2: Electrospray ionization mass spectrum of PF_6^- analogue of the self-assembled product in acetonitrile. (Inset) Experimental and calculated isotopic distribution pattern of the $[\text{C}_1 - 5\text{PF}_6]^{5+}$ fragment.



The stoichiometry and composition of the self-assembled product were conclusively established through electrospray ionization mass spectrometry (ESI-MS) analysis of the hexafluorophosphate (PF_6^-) analogue of the self-assembled product. The resulting spectrum exhibited several prominent peaks corresponding to multiply charged species, notably at m/z values of 549.7374, 688.6735, 897.0897, and 1244.4381. These peaks were assigned to the ionized forms $[\text{C}_1 - 6\text{PF}_6]^{6+}$, $[\text{C}_1 - 5\text{PF}_6]^{5+}$, $[\text{C}_1 - 4\text{PF}_6]^{4+}$, and $[\text{C}_1 - 3\text{PF}_6]^{3+}$, respectively (Figure 2). The observed isotopic patterns were in agreement with simulated patterns, thereby validating the proposed molecular structure (Figure S5). These results confirmed the M_6L_4 stoichiometry of cage, i.e., combination of six metal acceptors (**M**) with four ligands (**L**). The M_6L_4 stoichiometry can adopt either an octahedral or a double-square structure. The nature of the NMR spectrum of the major self-assembled product confirms that the resultant major product is an octahedron (**C**₁). In an octahedron, the ligand peaks of the cage are expected to show one set of peaks, similar to what is observed for the ligand, due to the higher symmetry. The two-fold splitting of the minor peaks observed in the ^1H NMR spectrum of the self-assembled product mixture showed a relative integration of 2:1, which is a characteristic feature of double-square coordination cages (**C**₂) (Figure S6).

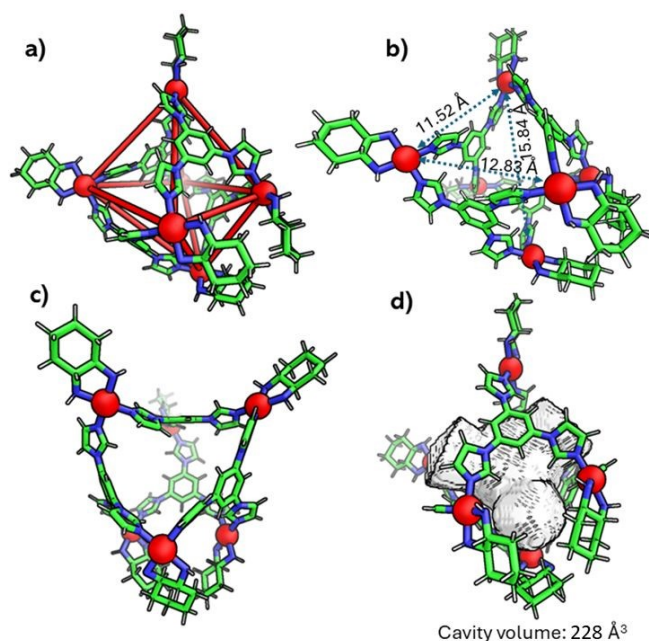


Figure 3: X-ray crystal structure of **C**₁ (CCDC No. 2455229). (a) Distorted octahedral shape of the cage, (b, c) side views of the cage, (d) cavity space of the cage (colour codes: C, green; N, blue; and Pd, red).

Finally, the geometry of **C**₁ was unambiguously confirmed through single-crystal X-ray diffraction (Figures 3 and S8-S11). Crystals appropriate for X-ray diffractions were obtained by the slow vapor diffusion of acetone into a saturated aqueous solution of the self-assembled product, in which nitrate (NO_3^-) was present as the counterion. Data collection was carried out using synchrotron

radiation. The compound **C**₁ crystallized in the triclinic space group P_1 and exhibited a distorted octahedral geometry. The asymmetric unit contains two crystallographically independent molecules which exhibit approximate inversion symmetry. However, analysis of the electron density indicated that P_1 is the correct space group, as converting from P_1 to P_{-1} gave rise to spurious electron density. With regard to the absolute configuration of the **M** acceptors (1*R*, 2*R*-dch), the calculated flack parameter was inconclusive.^{19a} However, Bayesian statistical analysis of Bijvoet pairs performed with PLATON confirmed the correctness of the assigned Table S2.^{19b}

The crystal structure revealed that four acceptor (**M**) units of each metallacage were arranged in a distorted square planar configuration. For one of the cages the distances of the four palladium ions from the mean plane of these same four palladium ions in the range 0.55-0.80 Å (see also Figure S9). Two additional acceptor units are situated on the axial positions, at vertical distances of 6.82 Å and 8.70 Å from the mean plane of the four equatorial palladium ions. The Pd...Pd distances between these two positions is 15.84 Å, thus the two ions are horizontally displaced with respect the equatorial mean plane. The overall result is a rather distorted octahedral architecture as shown in Figure 3a, 3b, 3c and Figure S9. Four ligands (**L**) occupy alternating faces of the octahedron. Additionally, the structure features a substantial internal cavity with triangular openings (as shown in Figure 3a, 3b, 3c and quantified in the ESI). The volume of the hydrophobic cavity of **C**₁ was calculated to be $228 \text{ \AA}^3$ (Figure 3d) by the MoloVol software.²⁰ The second metallacage exhibits very similar geometry characteristics. Further geometric details of the cages are outlined in the ESI. Geometry optimizations and single-point energy evaluations (B3LYP/def2-SVP, PCM) reveal that the octahedral M_6L_4 cage is $33.41 \text{ kcal}\cdot\text{mol}^{-1}$ more stable than the corresponding double-square assembly when constructed from the rigid *cis*-(1*R*, 2*R*-dch) Pd(II) corners. This substantial energy difference accounts for the formation of the octahedral topology (Figure S51a). Further, square-planar Pd(II) coordination ideally requires *cis* N-Pd-N angles of 90° . In the octahedral cage **C**₁, constructed from the rigid 1*R*,2*R*-cyclohexanediamine-based Pd(II) acceptor, the observed N-Pd-N angles are 84.19° and 91.30° , indicating only modest deviations from the ideal square planar geometry. These small distortions are readily accommodated within the octahedral M_6L_4 topology. In contrast, the DFT-optimized double-square cage **C**₂ constructed from the same rigid acceptor exhibits N-Pd-N angles of 79.96° and 103.65° , corresponding to large deviations from 90° and leading to significant geometric strain (Figure S51b). Additional insight is obtained by comparing the dihedral angles of the cyclohexanediamine-based Pd(II) acceptor in **C**₁ and **C**₂. The dihedral angles are 54.39° in octahedral **C**₁ and 56.45° in double-square **C**₂, showing only a very small difference. This minimal variation confirms the high rigidity of the 1*R*,2*R*-cyclohexanediamine chelate, which prevents the substantial conformational adjustment required for the double-square topology and therefore favours formation of the rigid octahedral architecture as the major product.



By contrast, in our previously reported double-square architecture assembled using the TMEDA–Pd(II) acceptor (**C**₃), the dihedral angle is only 4.03°, while a recently reported octahedral architecture (**C**₄) using the same TMEDA–Pd(II) acceptor shows a dihedral angle of 54.09°. These large variations clearly demonstrate that the TMEDA–Pd(II) acceptor is highly flexible, compared to rigid 1*R*,2*R*-cyclohexanediamine acceptor (Figure S51b).^{13a,b}

Guest Encapsulation Studies

The encapsulation ability of host **C**₁ was examined using aromatic guests **G**₁, **G**₂, **G**₃ and **G**₄ as model guest molecules (Figure 4). An excess amount of solid Thieno[3,2-*b*]thiophene (**G**₁) was introduced into an aqueous solution of **C**₁, followed by stirring at room temperature for 8 hours. This resulted in the formation of a cloudy mixture, which was subsequently centrifuged, and the clear supernatant was collected for further analysis. The resulting solution (**G**₁⊂**C**₁) displayed new proton signals in the ¹H NMR spectrum, appearing at 6.14 and 5.90 ppm (Figure 4b), which correspond to guest signals. Additionally, the protons on the imidazole rings were shifted downfield, while the benzene protons of the ligand shifted upfield, due to the host-guest interaction with the guest molecule. These chemical shift changes indicated successful encapsulation of guest within the cage cavity. Further confirmation of internal binding was obtained from the ¹H DOSY NMR spectrum of the **G**₁⊂**C**₁ complex in D₂O, which exhibited a single diffusion coefficient (log D = −9.844) (Figure S13), consistent with the formation of host-guest assembly. Evidence for spatial proximity between the host and guest was observed in the ¹H–¹H NOESY spectrum (Figure S14), where cross-peaks were observed between protons of the **C**₁ ligand and the aromatic protons of **G**₁. Host-guest stoichiometry was established through signal integration of the NMR spectra, indicating a 1:2 ratio between **C**₁ and **G**₁ (Figure S12). Additional analysis showed that **C**₁ encapsulated one molecule of **G**₂, two molecules of **G**₃ and one molecule of **G**₄ in separate experiments. (Figures S15–S18).

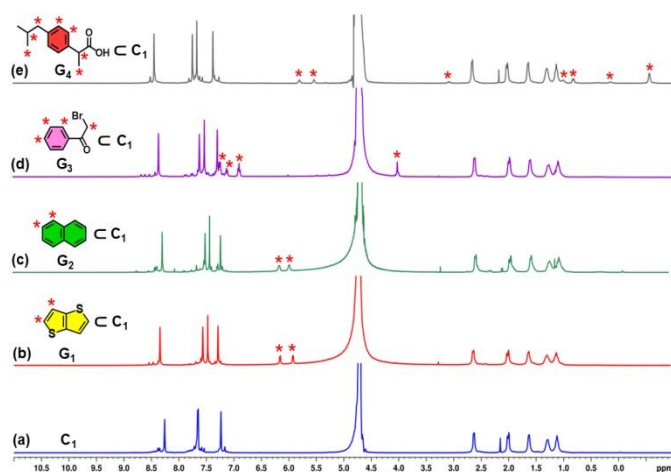


Figure 4. ¹H NMR spectra of (a) **C**₁, (b) **G**₁⊂**C**₁, (c) **G**₂⊂**C**₁, (d) **G**₃⊂**C**₁, and (e) **G**₄⊂**C**₁ in D₂O showing the change in NMR upon guest encapsulation by **C**₁. Star-marked peaks correspond to the encapsulated guests.

Having a water-soluble flexible octahedral host in hand, we sought to explore its potential for mediating chemical transformations in aqueous medium. Recent research by Dasgupta et al. demonstrated that photoactivation of terminal alkynes within a water-soluble, rigid Pd₆ octahedral nanocage (**TPT Cage**) occurs via a host-guest charge transfer (CT) mechanism, ultimately yielding C–C coupling products.²¹ In that system, photoinduced CT is followed by proton loss to generate a neutral radical intermediate, which is stabilized by the electron-deficient triazine-based ligand framework. Motivated by this strategy, we examined whether our structurally flexible, imidazole-based octahedral cage (**C**₁) could mediate photo-oxidation of the encapsulated substrates in a catalytic fashion. In contrast to the triazine system, **C**₁ incorporates a relatively electron-rich benzene-derived core, which we envisioned might alter the reactivity pathway of encapsulated terminal alkynes. Remarkably, instead of facilitating radical-mediated C–C coupling, **C**₁ directed the selective oxidation of terminal alkynes to carboxylic acids.

Oxidation of Terminal Alkynes to Corresponding Carboxylic Acid within **C**₁

Initially, we investigated whether ethynylbenzene (**R**₁) could be encapsulated in the cavity of **C**₁. An excess amount of **R**₁ was added to an aqueous solution of **C**₁ and stirred for 12 hours. The resulting solution was centrifuged and subjected to NMR analysis. The ¹H NMR spectrum showed downfield shift of the host peaks with the appearance of guest peaks in the aromatic region (Figure 5b). The ¹H DOSY NMR spectrum showed a single diffusion coefficient for the host and guest protons which confirmed the formation of an inclusion complex (Figure S20). Moreover, the ¹H–¹H NOESY spectrum (Figure S21) displayed distinct cross-peaks between the host and guest protons, providing strong evidence for guest encapsulation within the cage cavity. Furthermore, the host-guest stoichiometry of the **R**₁⊂**C**₁ complex was determined using ¹H NMR titration experiments. Cage **C**₁ was dissolved in D₂O, while a stock solution of the guest **R**₁ was prepared in MeOD-*d*₄. Incremental additions of 10 μL aliquots of the **R**₁ stock solution were made to the aqueous solution of **C**₁, and NMR spectra were recorded immediately after each addition (Figure S26a).

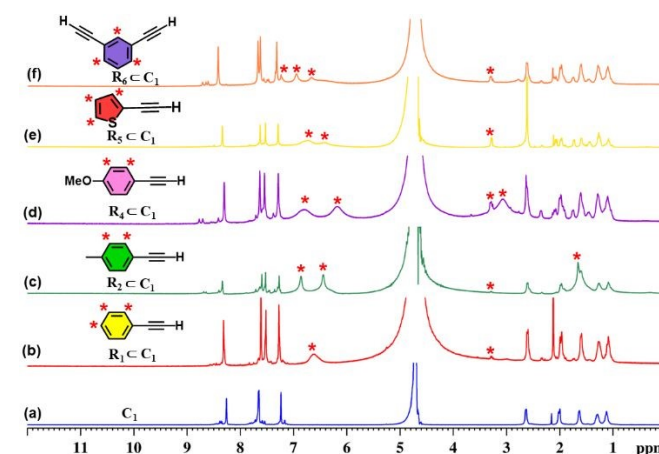


Figure 5. ^1H NMR stack plot of (a) C_1 , (b) R_1C_1 , (c) R_2C_1 , (d) R_4C_1 , (e) R_5C_1 , and (f) R_6C_1 , in D_2O showing the change in NMR upon guest encapsulation by C_1 . Star-marked peaks correspond to the encapsulated guests.

During the titration, continuous shifts in the proton signals of both host and guest were observed, indicating a fast exchange process on the NMR timescale. The stoichiometric ratio was established using a Job's plot, which confirmed a 1:2 host:guest ratio (Figure S27a). Similarly, we have studied the encapsulation of derivatives of terminal alkyne ($\text{R}_2\text{-R}_6$) like that of R_1 (Figures S22-S25).

The photocatalytic efficiency of cage C_1 was initially evaluated using ethynylbenzene (R_1) in water under 390 nm light irradiation. Remarkably, the targeted oxidative cleavage product P_1 was formed in 99% (GC yield) yield after 2 hours under aerobic conditions (Table 1, entry 2), highlighting the strong photocatalytic performance of C_1 . The individual acceptor and ligand components were used under the same conditions, but no product formation was detected (Table 1, entries 3–4). Alternative light sources, including blue LEDs (450 nm) and white LEDs, also failed to drive the oxidation, yielding no detectable products (Table 1, entry 6). Likewise, performing the reaction under thermal conditions or in the absence of light or photocatalyst led to no conversion (Table 1, entries 5, 7 and 8), confirming the necessity of both light and cage C_1 for the reaction to proceed. In addition, we prepared a water-soluble derivative of the ligand. Here, the three imidazole moieties of ligand L were methylated and converted to the nitrate salt to prepare the water-soluble cationic form (L_1) (Scheme S1). Notably, L_1 was unable to catalyse the reaction, highlighting the essential role of the cage C_1 in catalytic activity (Table 1, entries 13).




Table 1. Oxidation of Ethynylbenzene to Benzoic acid.

Entry	Solvent	Atmosphere	Temperature	Light (nm)	Time (h)	Cage /Acceptor/ Ligand	Yield (%)
1	H_2O	O_2	r. t.	390	2	Cage C_1	>99
2	H_2O	Air	r. t.	390	2	Cage C_1	>99
3	H_2O	Air	r. t.	390	2	Acceptor (M)	0
4	H_2O	Air	r. t.	390	2	Ligand (L)	0
5	H_2O	Air	r. t.	Dark	2	Cage C_1	0
6	H_2O	Air	r. t.	White/Blue	2	Cage C_1	0
7	H_2O	Air	Heat	-	2	Cage C_1	0
8	H_2O	Air	r. t.	390	2	BLANK	0
9	H_2O	Air	r. t.	390	2	C_1 +TEMPO	4
10	H_2O	Air	r. t.	390	2	C_1 +p-BQ	10
11	H_2O	Air	r. t.	390	2	C_1 +t-butanol	20

12	H_2O	Air	r. t.	390	2	C_2	0
13	H_2O	Air	r. t.	390	2	C_3	0
14	CH_3OH	Air	r. t.	390	2	L	0

Reactions were carried out in water at room temperature for 2 h under ambient atmosphere using 5 mol% cage (C_1) and 390 nm LED irradiation. Yields were determined by GC-MS after extraction with EtOAc.

To gain mechanistic insights, we initially recorded the UV-Vis absorption spectra of the host-guest complexes. A broad band emerged in the absorption spectra for the host-guest complexes, which was attributed to charge-transfer (CT) interactions between the guest and host molecules (Figure S28). Further, we carried out control experiments to study the reactive species generated during this transformation. In the presence of 2,2,6,6-tetramethylpiperidinyloxy (TEMPO), a known radical scavenger, the reaction yielded only trace amounts of the target product (Table 1, entry 9), implying a radical-mediated mechanism. Similarly, addition of p-benzoquinone, a quencher for superoxide radicals, suppressed product formation significantly (Table 1, entry 10). To assess the role of hydroxyl radicals as the reaction intermediate, tertiary butanol was used as an efficient hydroxyl radical trap under standard reaction conditions. This led to decrease in yield (Table 1, entry 11). The analysis of EPR results further confirmed the presence of the superoxide radical and hydroxyl radical in the reaction mixture (Fig. S47). The above-mentioned results clearly indicate that the reaction proceeds through the superoxide, which further reacts with the water to yield the hydroxyl radical.¹⁸

Based on our experimental observations, we propose a catalytic mechanism in which the supramolecular cage operates like an enzyme, facilitating chemical transformations within its confined space (Figure S48). Initially, the cage forms a strong charge transfer interaction with the ethynylbenzene, as verified by UV-Vis study. Upon irradiation with 390 nm UV light, an electron transfer (ET) occurs from the electron-rich aromatic guest to the cage interior, generating a terminal alkyne radical cation. Concurrently, molecular oxygen (O_2) is converted to superoxide anion ($\text{O}_2^{\bullet-}$), which subsequently reacts with water to yield hydroxyl radicals ($\bullet\text{OH}$) and hydroxide ions (OH^-). Subsequently, the terminal alkyne radical cation is attacked by $\bullet\text{OH}$ to generate a cationic intermediate (II), which then undergoes nucleophilic attack by OH^- to produce intermediate (III). These intermediate experiences a β -scission process, resulting in the formation of an aldehyde, which was confirmed through GC-MS analysis after 1 hour of irradiation of 1-ethynyl-4-methylbenzene (Figure S44). Continued oxidation of this aldehyde ultimately leads to the formation of a carboxylic acid.

To investigate whether the trace amount of double-square cage (C_2) formed in the self-assembly could contribute to the observed reactivity, control experiments were performed using a known double-square cage (C_3) that contains N,N,N',N'-tetramethylethylene-1,2-diamine blocked cis-Pd(II) acceptor. C_3 was used for this control experiment because C_2 couldn't be isolated as



ARTICLE

Journal Name

major species. The structurally similar (like **C**₂) double-square cage, **C**₃, previously reported^{13a} based on the same ligand framework, was synthesized (Figure S45) and tested under identical catalytic conditions (Figure S46). No product formation was observed with the **C**₃ cage, indicating that it is not catalytically active (Table 4, entry 12). To elucidate the distinct reactivities of the octahedral cage **C**₁ and the double-square cage **C**₃, we carried out UV-vis analyses with **R**₁. Whereas **C**₁ exhibits a clear charge-transfer band upon addition of phenylacetylene, **C**₃ shows no such response, despite possessing the same tritopic ligand. This unequivocally highlights the critical influence of cage topology in enabling substrate activation. The flexible double-square geometry of **C**₃ fails to provide the spatial and electronic confinement needed to stabilise the charge-transfer state, preventing initiation of the catalytic cycle. Consequently, **C**₃ remains catalytically inactive, and no oxidation product was observed (Figures S28b–S28c). These results strongly suggest that the catalytic activity arises exclusively from the **C**₁ cage, which features an octahedral geometry. Thus, neither the **C**₂ nor the **C**₃ cage appears to participate in the catalytic cycle.

Different Chemical Reactivity of Terminal Alkynes within **C**₁ and TPT Cage

To understand the reason behind the tendency of the octahedral TPT cage (containing 2,4,6-tris(4-pyridyl)-triazine ligand) to promote the C–C coupling product²¹ and **C**₁ to make the oxidized product, the structures of the host–guest complexes (i.e., **R**₁⊂TPT and **R**₁⊂**C**₁) were optimized by semiempirical methods with xTB programme (Figure 6).²² In the case of **C**₁, the optimized structure revealed that two phenylacetylene molecules are accommodated within the cavity, where they are stabilized primarily through π – π interactions with the electron-rich benzene walls of the cage, with a binding energy of –32.0 kcal/mol (Figure S52). Notably, the two guest molecules adopt an opposite orientation on either side of the cavity. This spatial arrangement precludes close approach of the alkyne moieties and effectively rules out radical–radical recombination, thereby disfavoring C–C bond formation. Instead, the electronic environment of **C**₁ channels reactivity toward oxidative transformations of the encapsulated substrates. In sharp contrast, the optimized **R**₁⊂TPT complex revealed that up to four phenylacetylene molecules can be preorganized within the rigid, electron-deficient triazine-based cavity (Figure S53). Stabilization in this case arises from π – π stacking interactions between the guest molecules and the triazine walls. Importantly, pairs of phenylacetylenes are oriented in the same direction relative to one another within the cavity, which brings their reactive sites into closer spatial proximity. Upon photoinduced charge transfer and subsequent proton loss, the resulting neutral radical intermediates are stabilized by the electron-deficient triazine framework. The combination of guest preorganization and radical stabilization provides a structural basis for the observed propensity of the TPT cage to promote C–C coupling (Figure 6b).

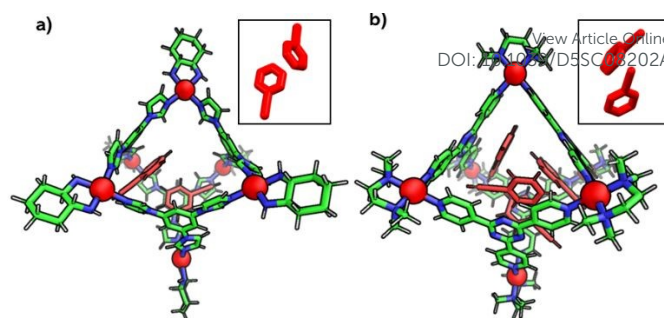












Figure 6. Optimized structures of preorganization of **R**₁ inside the cavity of (a) **C**₁ (Inset) showing opposite orientation of two **R**₁, (b) TPT cages (Inset) same orientation of two **R**₁ (optimized using xTB programme).

Moreover, in our previous work, we demonstrated that a water-soluble cage could promote the oxidation of methyl substituent in aromatic ring to carboxylic acids under mild, photocatalytic conditions.^{15f} Motivated by this reactivity, we sought to expand the scope to more terminal alkynes, specifically methyl-substituted phenylacetylenes, to probe whether both the methyl and the alkyne moieties might undergo oxidation inside the cage. We observed that only the alkyne functionality was oxidized, while the methyl group in the aromatic ring remained intact (Table 2, entry 1,2). This chemoselectivity suggests that the confined, electron-rich environment of **C**₁ uniquely channels the oxidation pathway towards alkyne activation. Extending this study to di-alkynyl substrates revealed that both alkyne groups could be cleanly transformed into carboxylic acids, further underscoring the distinct reactivity imparted by the cage (Table 2, entry 5). With the optimal conditions established, we explored the substrates scope for the transformation of terminal alkynes to corresponding carboxylic acids using **C**₁. A range of substituted alkynes bearing groups such as methyl- (**R**₂, **R**₃), methoxy- (**R**₄), thio- (**R**₅), and diethynyl (**R**₆) functionalities were tested, and the corresponding carboxylic acids were obtained in excellent yields, demonstrating the broad applicability of the system. Importantly, the water-soluble cage photocatalyst **C**₁ could be efficiently recovered post-reaction by simple in-flask extraction with ethyl acetate. This allowed for direct reuse of both the catalyst and aqueous solvent for subsequent reactions by adding a fresh batch of alkyne. The aqueous medium containing **C**₁ retained its catalytic activity over at least five consecutive cycles without measurable loss of efficiency (Figure S49). This highlights the sustainability of the system, where both the photocatalyst and reaction medium are recyclable without the need for removal from the reaction setup (Figure S50).



Table 2. Photocatalytic Oxidation of Various Ethynyl Aromatics.

Entry	Substrate	Condition	Time	Product	yield (%)
1		C ₁ (5 mol%) hν (390 nm)	2h		>99
2		C ₁ (5 mol%) hν (390 nm)	2h		>99
3		C ₁ (5 mol%) hν (390 nm)	2h		>99
4		C ₁ (5 mol%) hν (390 nm)	2h		>99
5		C ₁ (5 mol%) hν (390 nm)	2h		>99

All reactions were carried out in water at room temperature for 2 h under ambient atmosphere using 5 mol% cage (**C**₁) and 390 nm LED irradiation. Yields were determined by GC–MS after extraction with EtOAc.

To evaluate whether the proposed catalytic mechanism also applies to internal alkynes, we examined prop-1-yn-1-ylbenzene as a representative substrate under identical supramolecular cage reaction conditions. The reaction proceeded slowly (requiring ~10 h), and benzoic acid was obtained (Figure S41c). UV–vis measurements indicate that this internal alkyne forms weak charge-transfer complex with the cage **C**₁, which likely accounts for the reduced reactivity (Figure S28e). These results suggest that, although internal alkynes can undergo oxidation within the cage, the efficiency is diminished due to less favourable charge-transfer interaction.

Conclusion

We have successfully synthesized a new water-soluble Pd₆ octahedral nanocage (**C**₁) via coordination-driven self-assembly of a cis-blocked Pd(II) 90° acceptor (**M**) [**M** = cis-(1*R*, 2*R*-dch)Pd(NO₃)₂] with a triimidazole-based donor ligand (**L**). Formation of such an octahedral structure from a cis-blocked 90° acceptor, employing this tri-imidazole ligand **L**, is very unusual as the similar [4+6] self-assembly of **L** with the commonly-used 90° acceptor, cis-(tmeda)Pd(NO₃)₂, is known to form double-square architecture with similar composition.^{13a} Single-crystal X-ray diffraction confirms the formation of an unusual octahedral cage architecture as the major

self-assembled product. This octahedral cage showed excellent encapsulation of various aromatic molecules and terminal alkynes. Importantly, **C**₁ catalyses the selective photooxidative cleavage of terminal alkynes to carboxylic acids under mild aqueous conditions. The role of cage cavity of **C**₁ for this transformation was established by using an isomeric Pd₆ cage (**C**₃), which differs in the geometry, and a water-soluble ligand (**L**₁), both of which failed to produce desired product under the same conditions. Guest encapsulation within the nanocage cavity promotes the formation of charge-transfer complex, which upon photoexcitation generates a radical cation on the confined alkyne substrate as a reactive intermediate. Moreover, the difference in the reactivity of terminal alkynes in the cavities of **C**₁ and known **TPT** cages was examined by computational analysis. The theoretical studies showed that a combination of guest preorganization and radical stabilization is responsible for the difference in the observed chemical reactivity of terminal alkynes within the cavity of **C**₁ and **TPT** cage. Since the Pd centers in the nanocage do not directly engage in the chemical transformation, our findings establish a blueprint for developing supramolecular hosts for photocatalytic oxidations.

Conflicts of interest

There are no conflicts to declare.

Data availability

All data are provided in ESI† and additional data will be available upon request.

Acknowledgements

P.S.M. thanks the SERB-India for financial support as core research grant and as J.C. Bose fellowship. P.K.M. is grateful to PMRF (India) for fellowship.

References

- (a) C. H. Wong and G. M. Whitesides, *J. Am. Chem. Soc.*, 1982, **104**, 3542; (b) S. Martí, M. Roca, J. Andrés, V. Moliner, E. Silla, I. Tuñón and J. Bertrán, *Chem. Soc. Rev.*, 2004, **33**, 98; (c) P. Bajaj, G. Sreenilayam, V. Tyagi and R. Fasan, *Angew. Chem., Int. Ed.*, 2016, **55**, 16110; (d) M. Winkler, M. Geier, S. P. Hanlon, B. Nidetzky and A. Glieder, *Angew. Chem., Int. Ed.*, 2018, **57**, 13406; (e) T. Iqbal, S. Murugan and D. Das, *Sci. Adv.*, 2024, **10**(26), eaad12492.
- (a) R. Breslow and S. D. Dong, *Chem. Rev.*, 1998, **98**, 1997; (b) J. Meeuwissen and J. N. H. Reek, *Nat. Chem.*, 2010, **2**, 615; (c) X. Zhang, C. Yang, P. An, C. Cui, Y. Ma, H. Liu, H. Wang, X. Yan, G. Li and Z. Tang, *Sci. Adv.*, 2022, **8**, eadd5678; (d) H. Sepehrpour, W. Fu, Y. Sun and P. J. Stang, *J. Am. Chem. Soc.*, 2019, **141**, 14005; (e) Q. Feng, R. Li, T. Gao, D. Chu and M. Zhang, *Sci. China Chem.*, 2023, **66**, 2447.



- 3 (a) L. Ma, C. Abney and W. Lin, *Chem. Soc. Rev.*, 2009, **38**, 1248; (b) Z. Cheng, K. M. Fahy, G. W. Peterson, K. O. Kirlikovali and O. K. Farha, *Adv. Mater.*, 2025, **e2413848**; (c) J. Baek, B. Rungtaweevoranit, X. Pei, M. Park, S. C. Fakra, Y.-S. Liu, R. Matheu, S. A. Alshmimri, S. Alshehri, C. A. Trickett, G. A. Somorjai and O. M. Yaghi, *J. Am. Chem. Soc.*, 2018, **140**(51), 18208–18216; (d) P. Majumder, S. Mohata, H. S. Sasmal, B. Chandra, H. Kuiry and R. Banerjee, *Angew. Chem., Int. Ed.*, 2024, **63**(45), **e202412122**; (e) A. Basak, S. Karak and R. Banerjee, *J. Am. Chem. Soc.*, 2023, **145**(13), 7592–7599.
- 4 (a) Liu, C.; Liu, K.; Wang, C.; Liu, H.; Wang, H.; Su, H.; Li, X.; Chen, B.; Jiang, J., *Nat. Commun.*, 2020, **11**, 1047; (b) K. G. Andrews, T. K. Piskorz, P. N. Horton and S. J. Coles, *J. Am. Chem. Soc.*, 2024, **146**, 17887–17897; (c) J. Yang, S. Yu, W. Zhang, S. Yang, D. Hu, Y. Guan, H. Li and M. Liu, *Angew. Chem. Int. Ed.*, 2025, **64**, e202512561; (d) F. Würthner, C.-C. You and C. R. Saha Möller, *Chem. Soc. Rev.*, 2004, **33**(3), 133–146; (e) H. Li, Z.-J. Yao, D. Liu and G.-X. Jin, *Coord. Chem. Rev.*, 2015, **293–294**, 139–156; (d) T. Zhang, L.-P. Zhou, X.-Q. Guo, L.-X. Cai and Q.-F. Sun, *Nat. Commun.*, 2017, **8**, 15898; (e) Y.-Y. Zhang, X. Xu, H.-X. Li, L. Ma, M.-P. Song and H.-B. Yang, *Coord. Chem. Rev.*, 2016, **306**, 115–144; (f) Q.-Q. Yan, J. Tessarolo, S. Hasegawa, Z.-Y. Han, É. Benchimol, A. S. Mikherdov, C. Drechsler, J. J. Holstein, Y.-T. Chen, S. Ganta and G. H. Clever, *Small*, 2025, **e2500751**, 1–11.
- 5 (a) E. G. Percástegui, T. K. Ronson and J. R. Nitschke, *Chem. Rev.*, 2020, **120**(24), 13480–13544; (b) B. Huang, L. Mao, X. Shi and H. B. Yang, *Chem. Sci.*, 2021, **12**(41), 13648–13663; (c) R. Ham, C. J. Nielsen, S. Pullen and J. N. H. Reek, *Chem. Rev.*, 2023, **123**(9), 5225–5261; (d) T. K. Piskorz, V. Martí-Centelles, R. L. Spicer, F. Duarte and P. J. Lusby, *Chem. Sci.*, 2023, **14**(41), 11300–11331; (e) C. J. T. Cox, J. Hale, P. Molinska and J. E. M. Lewis, *Chem. Soc. Rev.*, 2024, **53**, 10380–10408.
- 6 (a) B. Breiner, J. K. Clegg and J. R. Nitschke, *Chem. Sci.*, 2011, **2**, 51; (b) B. Roy, A. Devaraj, R. Saha, S. Jharimune, K.-W. Chi and P. S. Mukherjee, *Chem. Eur. J.*, 2017, **23**, 15704; (c) D. M. Kaphan, M. D. Levin, R. G. Bergman, K. N. Raymond and F. D. Toste, *Science*, 2015, **350**, 1235; (d) V. Martí-Centelles, A. L. Lawrence and P. J. Lusby, *J. Am. Chem. Soc.*, 2018, **140**, 2862; (e) D. M. Kaphan, F. D. Toste, R. G. Bergman and K. N. Raymond, *J. Am. Chem. Soc.*, 2015, **137**, 9202.
- 7 (a) T. Mitra, K. E. Jelfs, T. Hasell, D. J. Adams, D. P. McMahon, S. Y. Chong, S. Brandani *et al.*, *Nat. Rev. Chem.*, 2021, **5**, 168–182; (b) M. Yamashina, M. Akita, T. Hasegawa, S. Hayashi and M. Yoshizawa, *Sci. Adv.*, 2017, **3**(8), **e1701126**; (c) K. Hema, A. B. Grommet, M. J. Biatek, J. Wang, L. Schneider, C. Drechsler, O. Yanshyna, Y. Diskin Posner, G. H. Clever and R. Klajn, *J. Am. Chem. Soc.*, 2023, **145**(45), 24755–24764; (d) Z. Lu, T. K. Ronson, A. W. Heard, S. Feldmann, N. Vanthuyne, A. Martinez and J. R. Nitschke, *Nat. Chem.*, 2023, **15**, 405–412; (e) W. M. Bloch, S. Horiuchi, J. J. Holstein, C. Drechsler, A. Wuttke, W. Hiller, R. A. Mata and G. H. Clever, *Chem. Sci.*, 2023, **14**, 1524–1531; (f) K. Li, L.-Y. Zhang, C. Yan, S.-C. Wei, M. Pan, L. Zhang and C.-Y. Su, *J. Am. Chem. Soc.*, 2014, **136**(12), 4456–4459.
- 8 (a) P. K. Maitra, S. Bhattacharyya, P. C. Purba and P. S. Mukherjee, *Inorg. Chem.*, 2024, **63**(5), 2569–2576; (b) L. A. Pérez Márquez, M. D. Perretti, R. García Rodríguez, F. Lahoz and R. Carrillo, *Angew. Chem., Int. Ed.*, 2022, **61**(28), **e202205403**; (c) A. Baby Sainaba, R. Saha, M. Venkateswarulu, E. Zangrando and P. S. Mukherjee, *Inorg. Chem.*, 2024, **63**(1), 508–517; (d) M. Zhang, M. L. Saha, M. Wang, Z. Zhou, B. Song, C. Lu, X. Yan, X. Li, F. Huang, S. Yin and P. J. Stang, *J. Am. Chem. Soc.*, 2017, **139**(14), 5067–5074; (e) H.-Y. Lin, L.-Y. Zhou and L. Xu, *Chem. Asian J.*, 2021, **16**(23), 3805–3816.
- 9 (a) C. M. Hong, D. M. Kaphan, R. G. Bergman, K. N. Raymond and F. D. Toste, *J. Am. Chem. Soc.*, 2017, **139**(23), 8013–8021; (b) R. Gera, P. De, K. K. Singh, S. A. V. Jannuzzi, A. Mohanty, L. Velasco, Kulbir, P. Kumar, J. F. Marco, K. Nagarajan, C. Pecharromán, P. M. Rodríguez Pascual, S. DeBeer, D. Moonshiram, S. Sen Gupta and J. Dasgupta, *J. Am. Chem. Soc.*, 2024, **146**(31), 21729–21741; (c) P. J. Boaler, T. K. Piskorz, L. E. Bickerton, J. Wang, F. Duarte, G. C. Lloyd-Jones and P. J. Lusby, *J. Am. Chem. Soc.*, 2024, **146**(28), 19317–19326; (d) R. G. DiNardi, S. Rasheed, S. S. Capomolla, M. H. Chak, I. A. Middleton, L. K. Macreadie, J. P. Violi, W. A. Donald, P. J. Lusby and J. E. Beves, *J. Am. Chem. Soc.*, 2024, **146**(31), 21196–21202; (e) H. Vardhan and F. Verpoort, *Adv. Synth. Catal.*, 2015, **357**(7), 1351–1368.
- 10 (a) D. Prajapati, P. Bhandari, E. Zangrando and P. S. Mukherjee, *Chem. Sci.*, 2024, **15**, 3616–3624; (b) D. Zhang, T. K. Ronson, R. Lavendomme and J. R. Nitschke, *J. Am. Chem. Soc.*, 2019, **141**(48), 18949–18953; (c) A. Baby Sainaba, M. Venkateswarulu, P. Bhandari, K. S. A. Arachchige, J. K. Clegg and P. S. Mukherjee, *J. Am. Chem. Soc.*, 2022, **144**(16), 7504–7513; (d) L.-J. Wang, S. Bai, Y.-F. Han and J. Li, *J. Am. Chem. Soc.*, 2022, **144**(35), 16191–16198; (e) Y. Du, A. Ghosh, P. C. P. Teeuwen, D. J. Wales and J. R. Nitschke, *J. Am. Chem. Soc.*, 2025, **147**(23), 12123–12132.
- 11 (a) Y. Hou, Z. Zhang and M. Zhang, *Acc. Chem. Res.*, 2025, **58**(8), 1644–1655; (b) Y. Li, S. S. Rajasree, G. Y. Lee, J. Yu, J.-H. Tang, R. Ni, G. Li, K. N. Houk, P. Deria and P. J. Stang, *J. Am. Chem. Soc.*, 2021, **143**(7), 2908–2919; (c) P. C. Purba, P. K. Maitra, S. Bhattacharyya and P. S. Mukherjee, *Inorg. Chem.*, 2023, **62**(28), 11037–11043; (d) D. Bokotial, K. Acharyya, A. Chowdhury and P. S. Mukherjee, *Angew. Chem., Int. Ed.*, 2024, **63**(18), **e202401136**; (e) D. Li, L. Yang, W. Fang, X. Fu, H. Li, J. Li, X. Li and C. He, *Chem. Sci.*, 2023, **14**, 9943–9950.
- 12 (a) M. Yoshizawa, M. Tamura and M. Fujita, *Science*, 2006, **312**, 251–254; (b) M. M. J. Smulders and J. R. Nitschke, *Chem. Sci.*, 2012, **3**, 785–788; (c) J. Chen, Y.-H. Huang, J. Yang, Y. Huang, Y.-L. Lu, Z. Jiao and C.-Y. Su, *J. Am. Chem. Soc.*, 2024, **146**(47), 32738–32747; (d) J. Chen, Y.-L. Lu, Y. Huang, F. Zhang, H. Ye, Y.-H. Huang, X.-D. Zhang, Z. Jiao and C.-Y. Su, *J. Am. Chem. Soc.*, 2025, **147**(15), 13008–13016; (e) G. R. Genov, H. Takezawa, H. Hayakawa and M. Fujita, *J. Am. Chem. Soc.*, 2023, **145**(31), 17013–17017; (f) J.-S. Wang, K. Wu, C.-Z. Yin, K. Li, Y.-H. Huang, J. Ruan, X. Feng, P. Hu and C.-Y. Su, *Nat. Commun.*, 2020, **11**, 4675.
- 13 (a) D. Samanta, S. Mukherjee, Y. P. Patil and P. S. Mukherjee, *Chem. Eur. J.*, 2012, **18**, 12322–12329; (b) K. Hema, A. B. Grommet,



M. J. Bialek, J. Wang, L. Schneider, C. Drechsler, O. Yanshyna, Y. Diskin-Posner, G. H. Clever and R. Klajn, *J. Am. Chem. Soc.*, 2023, **145**, 22347–22356; (c) Y. Qiao, L. Zhang, J. Li, W. Lin and Z. Wang, *Angew. Chem., Int. Ed.*, 2016, **55**(41), 12778–12782; (d) C. Liang, J. Yuan, C. Zhu and Y. Fang, *Catal. Today*, 2022, **400–401**, 75–82; (e) F. F. Zhu, L.-J. Chen, H.-B. Yang, C.-P. Hou, T. Wang, S. Wang, L. Jiang, H. Sun and C.-Y. Su, *Chem*, 2020, **6**(9), 2395–2406; (f) T.-P. Sheng, C. He, Z. Wang, G.-Z. Zheng, F.-R. Dai and Z.-N. Chen, *CCS Chem.*, 2022, **4**, 1098–1107; (g) Y. Qiao, L. Zhang, J. Li, W. Lin and Z. Wang, *Angew. Chem., Int. Ed.*, 2016, **55**(41), 12778–12782.

14 (a) M. R. Crawley, D. Zhang and T. R. Cook, *Inorg. Chem. Front.*, 2023, **10**, 316–324; (b) L.-X. Cai, S.-C. Li, D.-N. Yan, L.-P. Zhou, F. Guo and Q.-F. Sun, *J. Am. Chem. Soc.*, 2018, **140**, 4869–4876; (c) S. Pullen, S. Löffler, A. Platzek, J. J. Holstein and G. H. Clever, *Dalton Trans.*, 2020, **49**, 9404–9410; (d) E. O. Bobylev, D. A. Poole III, B. de Bruin and J. N. H. Reek, *J. Am. Chem. Soc.*, 2022, **144**, 15633–15642; (e) V. A. Rinshad, S. Ali, N. Hickey and P. S. Mukherjee, *Inorg. Chem.*, 2025, **64**(11), 5619–5627; (f) C. García Simón, R. Gramage Doria, S. Raoufmoghaddam, T. Parella, M. Costas, X. Ribas and J. N. H. Reek, *J. Am. Chem. Soc.*, 2015, **137**(7), 2680–2687.

15 (a) A. Das, I. Mandal, R. Venkatramani and J. Dasgupta, *Sci. Adv.*, 2019, **5**(2), eaav4806; (b) P. Cheng, L. Cai, D. Yan, L. Zhou and Q. Sun, *Catalysts*, 2021, **11**(4), 484; (c) P. K. Maitra, S. Bhattacharyya, N. Hickey and P. S. Mukherjee, *J. Am. Chem. Soc.*, 2024, **146**(22), 15301–15308; (d) J. Guo, Y.-W. Xu, K. Li, L.-M. Xiao, S. Chen, K. Wu, X.-D. Chen, Y.-Z. Fan, J.-M. Liu and C.-Y. Su, *Angew. Chem., Int. Ed.*, 2017, **56**(14), 3852–3856; (e) D.-N. Yan, L.-X. Cai, S.-J. Hu, Y.-F. Zhou, L.-P. Zhou and Q.-F. Sun, *Angew. Chem., Int. Ed.*, 2022, **61**(42), e202209879; (f) V. A. Rinshad, M. Aggarwal, J. K. Clegg and P. S. Mukherjee, *JACS Au*, 2024, **4**(8), 3238–3247.

16 (a) H. Liu, Y. Zhang and G. Chen, *Eur. J. Med. Chem.*, 2025, **273**, 116300; (b) L. Wang, D. Zhao and P. Xu, *J. Agric. Food Chem.*, 2024, **72**, 10852–10860; (c) X. Zhang, Q. Zhao and E. Y.-X. Chen, *J. Am. Chem. Soc.*, 2025, **147**, 10321–10329.

17 (a) K. A. Aravinda Kumar, V. Venkateswarlu, R. A. Vishwakarma and S. D. Sawant, *Synthesis*, 2015, **47**(20), 3161–3168; (b) B. C. Ranu, S. Bhadra and L. Adak, *Tetrahedron Lett.*, 2008, **49**(14), 2503–2506; (c) S. Bertini, D. Henryon, A. J. F. Edmunds and M. Albrecht, *Org. Lett.*, 2022, **24**(6), 1378–1382; (d) Q. Feng, Y. Wang, B. Zheng and S. Huang, *Org. Lett.*, 2023, **25**(1), 293–297.

18 R. Jia, J. Wang, Y. Jiang, B. Ni and T. Niu, *Org. Biomol. Chem.*, 2022, **20**, 8305–8312.

19 (a) H. D. Flack, *Acta Cryst.*, 1983, **A39**, 876–881; (b) A. L. Spek, *Acta Cryst.*, 2009, **D65**, 148–155.

20 J. B. Maglic and R. Lavendomme, *J. Appl. Crystallogr.*, 2022, **55**(4), 1033–1044.

21 D. Roy, S. Paul and J. Dasgupta, *Angew. Chem., Int. Ed.*, 2023, **62**, e202312500.

22 C. Bannwarth, S. Ehlert and S. Grimme, *J. Chem. Theory Comput.*, 2019, **15**(3), 1652–1671.

DOI: 10.1039/D5SC08202A



All data are provided in ESI and additional data can be available upon request.

[View Article Online](#)

DOI: 10.1039/D5SC08202A

