Energy & Environmental Science



PAPER

View Article Online



Cite this: DOI: 10.1039/d5ee01250d

Transition metal coordination to degradation products in battery electrolytes revealed by NMR and EPR spectroscopy

Jennifer P. Allen, ^{Dab} Conrad Szczuka, ^{Dcd} Erlendur Jónsson, ^{Da} Rüdiger-A. Eichel, ^{Cd} Josef Granwehr ^{Cd} and Clare P. Grey *

The dissolution of transition metals from lithium-ion battery materials contributes to cell failure. Developing a better understanding of transition metal solvation, reactivity, and deposition will help mitigate transition metal dissolution and, thus, facilitate batteries with higher capacity and longer lifetime. In this work, Mn²⁺ and Ni²⁺ coordination in degraded LiPF₆ carbonate electrolyte solutions is examined via 1 H and 19 F NMR relaxometry at ambient temperatures and pulsed (double resonance HYSCORE and ENDOR) EPR spectroscopy of the frozen solutions. Critically, the solvation spheres of transition metals in heat-degraded electrolytes are shown to differ from those found in pristine electrolytes, with significant coordination to LiPF₆-derived fluorophosphate degradation species—a factor that will impact the mechanisms and the extent of transition metal dissolution. The Mn²⁺ coordination environment is shown to be affected by adding a variety of species including water, ethylene glycol, and acetylacetonate, increasingly displacing EC and PF₆⁻ from inner and outer Mn²⁺ coordination shells. EPR and NMR studies of electrolytes containing the battery additive and proposed degradation product LiPO₂F₂ explicitly confirm that the transition metals coordinate to $PO_2F_2^-$ in both the inner and outer sphere. By contrast, in heat-degraded electrolytes, additional protonated (uncharged) fluorophosphate species are also present in the metal solvation shell, as clearly demonstrated via large ¹H and ³¹P hyperfine interactions, seen in the EPR spectra of Mn²⁺ complexes. To probe transition metal deposition, Mn²⁺ and Ni²⁺ were exposed to a wide variety of salts found in the solid electrolyte interphase (SEI), revealing for the first time that the metathesis deposition pathway is viable with many different SEI species.

Received 3rd March 2025, Accepted 9th October 2025

DOI: 10.1039/d5ee01250c

rsc.li/ees

Broader context

The dissolution of transition metal ions from essentially all battery cathode active materials is thought to be a significant cause of battery capacity fade. Dissolution can occur as part of cathode degradation processes, and these dissolved transition metals will cross over from cathode to anode, where they may precipitate, potentially contributing to breakdown of the passivating layer that forms on the graphite anode (the solid electrolyte interphase). Surprisingly, little is known about how the transition metals dissolve in battery electrolytes, from the pristine to the more degraded solutions that are representative of practical systems. In order to develop strategies to mitigate dissolution, including the design of new additives, coatings, and electrolytes, a fundamental understanding of how the relevant transition metals are dissolved in both pristine and degraded electrolytes is required. This paper attacks the issue directly by developing new magnetic resonance approaches to study these electrolytes and shows clearly that the coordination of these ions in degraded electrolytes is very different from coordination in the pristine electrolytes, and that these ions are strongly coordinated to a series of anions often found in degraded electrolytes and additives.

Introduction

While the dissolution of transition metals from battery cathode active materials is thought to cause significant battery capacity fade *via* a myriad of different mechanisms, ¹⁻⁶ comparatively little work has been performed to study the solvation of the transition metals once they are dissolved in the battery electrolyte solution.⁷⁻¹¹ Even less attention has been paid to how the

^a Yusuf Hamied Department of Chemistry, University of Cambridge, Lensfield Road, Cambridge, CB2 1EW, Cambridge, UK. E-mail: cpg27@cam.ac.uk

b The Faraday Institution, Quad One, Harwell Science and Innovation Campus, Didcot OX11 ORA, UK

^c Institute of Energy Technologies (IET-1), Forschungszentrum Jülich GmbH, 52425 Jülich, Germany

^d Institute of Physical Chemistry, RWTH Aachen University, 52056 Aachen, Germany

^e Institute of Technical and Macromolecular Chemistry, RWTH Aachen University, 52056 Aachen, Germany

solvation may differ between ideal pristine electrolyte solutions and (partly) degraded electrolyte solutions that more accurately represent the use case, particularly in regimes where the rate of transition metal dissolution is enhanced. Although an understanding of the transition metal solvation shell is not generally directly relevant to the bulk properties of the electrolyte solution, transition metal solvation and desolvation are important for transition metal dissolution and deposition behaviour. respectively. For example, a study of metal dissolution in LiNi_{0.5}Mn_{1.5}O₄/graphite cells proposed that solvent oxidation at the cathode surface generates β-diketonate species that are adsorbed on the surface, chelating the transition metals and facilitating metal dissolution. 12 Another study proposed that the chelation of dissolved Mn²⁺ by unspecified electrolyte degradation products may create neutral Mn complexes that can be transported through the outer, organic layer of the solid electrolyte interphase (SEI) and deposited at the surface of the inner, inorganic SEI.¹³ One density functional theory (DFT) study showed that P-F bonds in PF₆ were longer in the presence of Mn²⁺, facilitating the formation of MnF⁺ and the reactive Lewis acid, PF₅.8 In combination with experiments showing severe discolouration of electrolyte solutions stored with Mn^{2+,8,14} this suggests that dissolved transition metals may actually contribute to bulk electrolyte decomposition reactions even before their deposition at the anode occurs.

The process of transition metal dissolution may be driven by or coupled with electrolyte decomposition reactions occurring at the cathode; for instance, acidic oxidation or hydrolysis products may leach transition metals from the cathode. 12,15-20 Thus, when transition metal dissolution occurs, it is likely that the electrolyte solution is already degraded to some degree, and it is therefore vital to consider how transition metals are then solvated in the degraded electrolyte solution. However, computational studies of transition metal coordination in battery electrolyte solutions have largely focused on the components of the pristine electrolyte.7,8 One simulation study of Mn2+ dissolution processes incorporated ethylene carbonate (EC) decomposition products and F on the modelled LiMn₂O₄ (LMO) surface, but simulated the electrolyte solution as 32 EC molecules. 21 Notably, modelling studies that have incorporated coordinating degradation species have shown that they do have an effect: one study incorporated F into a diethyl carbonate solution and found that F may facilitate the dissolution of Ni and Mn from LiNi_{0.5}Mn_{1.5}O₄ (LNMO);²² another simulation study found that biacetyl complexation at the surface of LiNixMnvCo1-x-vO2 (NMC) increased Ni dissolution, which was then confirmed experimentally.23 This is further supported by an experimental study showing enhanced dissolution from charged LiNi_{0.5}Mn_{0.3-} Co_{0.2}O₂ (NMC532) cathodes stored with a solution containing the salt lithium acetylacetonate (Li(acac)), as compared to the control electrolyte containing LiPF₆.²⁴ Another study found that transition metals dissolved from delithiated cathode materials in the presence of carbonate solvents tended to coordinate to anionic species. 10 Operando studies have shown that exposure of cathode materials to water-contaminated electrolyte solutions enhanced transition metal dissolution, 25 while exposure to

thermally degraded electrolyte solutions did not appear to enhance transition metal dissolution, complicating the picture.²⁶ If transition metals are indeed coordinated to degradation products in solution, whether thermally, chemically, or electrochemically generated, then models of how dissolution (solvation) and deposition (desolvation) occur may benefit from the incorporation of soluble electrolyte decomposition species in the simulated electrolyte solution. Although simulation of additional components is increasingly computationally expensive, targeted experiments may serve as a basis for computational work by identifying the solution species that are most likely to affect transition metal dissolution.

The role of PF₆⁻ degradation products in battery chemistry is complex. While alkylfluorophosphates have been proposed to trigger autocatalytic decomposition of the electrolyte solution,²⁷ and while difluorophosphate generated in situ may serve as an indicator of PF₆ hydrolysis, ²⁸⁻³¹ difluorophosphate itself does not appear to be harmful in cells: studies using a small percentage of added LiPO₂F₂ in the electrolyte solution have shown that it enhances cell performance³²⁻³⁸ by modifying the SEI at the cathode^{33,34,37,38} and anode^{34,36,37} surfaces, offering protective benefits, such as minimising impedance growth. With respect to transition metal dissolution, previous work has shown that added LiPO2F2 results in lower levels of transition metals deposited at the negative electrode. 32-35 It has been proposed that the PO₂F₂⁻ additive may decompose into PO₄³⁻ and PO₃F²⁻, which may induce precipitation of dissolved metals before they migrate to the anode (presumably at the cathode or in the separator). 32,35,39-41

Another pathway to prevent transition metal deposition, rather than inducing precipitation of transition metals before they reach the anode, involves sequestering them in solution. Chelating agents have been added to cells to prevent the deposition of dissolved metals by modifying the electrolyte solution, separator, or anode. In the electrolyte solution, transition metals have been sequestered by using crown ether,14 azacrown ether, 42 or 1,2-bis(diphenylphosphino)ethane 43 additives, or a specialised chelating polymer gel electrolyte. 44 Highly concentrated electrolyte solutions have been suggested to prevent the deposition of dissolved Mn2+ by increasing the formation of contact ion pairs and aggregates, in turn decreasing the favourability of incorporation in the SEI. 9 Numerous functionalised separators have been employed to trap dissolved transition metals in cells, with varying degrees of selectivity and efficiency, 45,46 and at the negative electrode, an aza-crown ether functionalised binder has been proposed.42 Chelating agents have also been used in the cathode to coordinate the metals and prevent dissolution into the electrolyte solution, for example, by functionalising the cathode binder^{47–50} or conductive carbon.⁵¹ The effects of transition metal chelation in lithiumion cells are complex, and it may be beneficial or harmful, depending on the context. Storage with 3:7 ethylene carbonate: ethyl methyl carbonate (EC: EMC, w/w) solution containing lithium acetylacetonate, Li(acac), has been shown to enhance Mn and Co dissolution (not Ni dissolution) from charged NMC532, although dissolution from pristine cathodes

was unaffected.²⁴ However, acetylacetone has also been used to chelate Mn and prevent its dissolution from LMO spinel: rinsing electrode materials with an acac solution and then sintering the materials was found to reduce Mn dissolution.^{52,53} This strategy succeeded because the acac solution leached Mn from the LMO surface, creating a Mn-deficient surface layer that was less prone to dissolution.^{52,53} These results suggest that an understanding of chelation is important and can directly be used to prevent cell degradation.

Generally, it is not entirely clear what fraction of transition metals remains in the electrolyte as soluble complexes and what fraction precipitates at the cathode or deposits at the anode, and how this is affected by the species present in solution, motivating further studies. In a cell, where many species are present simultaneously, it is difficult to predict how the formation of soluble chelate complexes may impact metal deposition. Both strategies outlined above, of inducing transition metal precipitation at the cathode and of sequestering metal ions in solution, target the prevention of metal deposition at the anode, and both strategies require an understanding of transition metal solvation, complexation, and desolvation behaviours.

In this work, we study the coordination of Mn²⁺ and Ni²⁺ in a degraded carbonate-based electrolyte. These species are of interest because Mn2+ is thought to be more harmful to cells than other dissolved metals, 3,5,54-56 and Ni²⁺ is the most abundant metal in nickel-rich lithium-ion battery cathode materials; both ions represent typical divalent^{5,20,57-60} paramagnetic dissolved transition metal ions. Mn²⁺ and Ni²⁺ species are studied separately in this work, such that results may be applicable to any chemistry containing either ion, including NMC, LMO, LNMO, LiNi_xCo_yAl_{1-x-y}O₂ (NCA), LiNiO₂ (LNO), $LiMn_xFe_{1-x}PO_4$ (LMFP), etc. The paramagnetism of these ions can be exploited to examine interactions between electron and nuclear spins, i.e., hyperfine interactions, using the complementary techniques of electron paramagnetic resonance (EPR) and nuclear magnetic resonance (NMR) spectroscopy, as illustrated in our previous publication on pristine electrolytes.¹¹ Pulsed EPR identifies nearby magnetically-active nuclei through their effect on the paramagnetic centre's electronic spin states, whereas paramagnetic NMR probes the nuclear spins' relaxation driven by nearby paramagnetic centres. Since the nuclear spins relax on a slower timescale than electron spins, the electron-nuclear (hyperfine) interactions can be studied via pulsed EPR experiments. These hyperfine interactions are described by interaction tensors represented through the coupling constants A_x , A_y , and A_z . A non-zero isotropic component $(A_x + A_y + A_z)/3$ indicates electron spin density at the position of the nucleus, generally implying that an inner sphere (bonded) complex is formed, and an anisotropic part describes all through-space dipolar contributions from both inner and outer sphere complexes. Cryogenic temperatures are typically required for pulsed EPR experiments, resulting in a loss of dynamic information, but instead allowing the static compositions and conformations of the transition metal complexes to be determined. EPR studies of the Ni2+ ion with its

S=1 electron spin are, however, difficult due to its rapid electronic relaxation. Paramagnetic NMR spectroscopy complements the EPR method because it can be carried out at ambient temperatures, encoding information on dynamics, and may be used to indirectly characterise the solvation shell of most paramagnetic transition metals, with direct relevance here for Ni²⁺. 62

The coordination sphere of Mn²⁺ and Ni²⁺ in degraded carbonate-based electrolytes is approached in two ways in this work. First, transition metal-containing electrolytes are heated and subsequently examined by pulsed EPR and NMR spectroscopy. Second, transition metal coordination to externally added species is investigated, including difluorophosphate, 28-32 water, ^{10,63-67} acac⁻, ¹² and ethylene glycol (EG), ⁶⁸⁻⁷⁰ because these and related species have been proposed to form, and/or coordinate to transition metals, in degraded battery electrolytes. EG is a hydrolysis product of EC,68,69 and some of the authors have previously proposed the dianion's role in vanadyl coordination in V⁴⁺-containing solutions.⁷⁰ Lithium difluorophosphate is also commonly used as an electrolyte additive or co-salt. 37,71 In pristing electrolytes, the transition metal solvation shell is largely comprised of EC;^{7,8,11} however, we show herein by using a combination of EPR and NMR spectroscopies that the solvation shell differs noticeably in degraded electrolytes. Neutral degradation species such as water and ethylene glycol appear to displace ethylene carbonate, while some PF₆ remains, largely in the outer solvation shell, at ambient temperature for charge balance. Anionic species such as PO₂F₂⁻, which was observed to form upon heating of electrolyte solutions, and acac appear to have a strong binding affinity and displace both EC and PF₆⁻ from the Mn²⁺ coordination shell. The effect of dissolved Mn2+ toward enhancing electrolyte decomposition, which has been previously proposed, 8,14 is then studied with NMR spectroscopy.

We use heat-treated electrolyte solutions to simulate electrolyte degradation, rather than sourcing cycled electrolytes from lithium-ion cells for the following key reasons. Firstly, using electrolytes from lithium-ion cells would cause various changes to the electrolyte composition that could have significant effects on the measured paramagnetic relaxation enhancement. The most notable of these is, of course, transition metal dissolution, both from the cathode in the lithium-ion cell and the cell casing.⁷² It would not be possible in this way to obtain an electrolyte that contained only Mn2+ or only Ni2+. Furthermore, electrolyte degradation reactions in the cell would result in changes to the salt concentration, solvent species, and viscosity that would in turn skew the baseline relaxation. The final reason is a practical limitation of the electrolyte volume: NMR relaxometry experiments used 500 µL of undiluted electrolyte (rather than a small volume of electrolyte in a large volume of deuterated solvent), preventing the use of electrolytes extracted from small-scale cells. Had many cells been used to gather a sufficient quantity of degraded electrolyte for all NMR experiments, there would be differences in the electrolyte extracted from each cell, leading to inconsistency between samples. In this case, it was our judgement that adding pristine electrolyte to a sealed container (a closed system) and heating it

shows that it is specifically and necessarily the generation of degradation products that is affecting the transition metal solvation, which is later explored through the addition of LiPO₂F₂. Nevertheless, building on the insights obtained from the results described below, future studies will focus on incorporating electrochemically-degraded electrolyte solutions sourced from full cells.

Lastly, we explore the deposition of transition metals in the SEI by metathesis, a mechanism that has been suggested for dissolved Mn²⁺,^{73–76} Ni²⁺,^{77,78} and Co²⁺;⁷⁹ even Li⁺ is known to exchange with other Li⁺ in the SEI. 80 Ex situ ion exchange experiments have shown by ion chromatography that Li₃PO₄ addition³⁹ and Na₂PO₃F addition⁴⁰ cause precipitation of Mn²⁺ Ni²⁺, and Co²⁺ from electrolyte solutions. Inductively coupled plasma mass spectrometry (ICP-MS) exchange experiments have shown Mn²⁺ precipitation from electrolyte solutions upon addition of Li₂O, LiF, and Li₂CO₃;⁷⁵ Mn²⁺ exchange with the latter two salts is further supported by XPS analysis.⁷⁴ Thus, the effect of a large series of lithium salts-some of which have been shown to be present in the SEI—on transition metal solubility was investigated in this work. Specifically, we examine the precipitation rates of Mn²⁺ and Ni²⁺ using inductively coupled plasma optical emission spectroscopy (ICP-OES) following exposure to 12 different organic and inorganic lithium salts.

Materials and methods

Preparation of electrolyte solutions

The bis(trifluoromethane)sulfonimide (TFSI) salts Mn(TFSI)₂ (Solvionic, 99.5%) and Ni(TFSI)₂ (Alfa Aesar, \geq 97%) were used to model transition metals dissolved from battery cathodes. EPR samples used concentrations of 8 mM Mn(TFSI)₂ and NMR samples used concentrations of 1 mM Mn(TFSI)2 and 1 mM Ni(TFSI)₂, except where specified otherwise. The main electrolyte solution used in this work comprised 1 M LiPF₆ in 3:7 ethylene carbonate: ethyl methyl carbonate (EC: EMC, v/v). For NMR experiments, this was sourced premixed (soulbrain MI PuriEL R&D 280); for EPR experiments, all solutions were mixed in-house using LiPF₆ (Sigma Aldrich, ≥99.99% trace metals basis), EC (Sigma Aldrich, 99%, anhydrous), and EMC (Sigma Aldrich, 99%). Owing to the different electrolyte sources, it is likely that EPR samples contained more water impurities than the NMR samples. EPR experiments also used 1 M LiTFSI (Alfa Aesar, 98+%) in 3:7 EC: EMC, mixed in-house. To mimic electrolyte degradation, samples were heat-treated (at either 35 $^{\circ}$ C or 45 $^{\circ}$ C for EPR samples and 60 $^{\circ}$ C for NMR samples) or underwent addition of LiPO₂F₂ (American Elements, 99%, recrystallised in-house), lithium acetylacetonate (Li(acac), Sigma Aldrich, 97%), distilled H₂O/D₂O (Sigma Aldrich, 99.9 atom%), and ethylene glycol (Sigma Aldrich, 99.8%, anhydrous). Additionally, deuterated dimethyl sulfoxide (d₆-DMSO, Sigma Aldrich, NMR-grade), methanol (MeOD, Sigma Aldrich, NMR-grade), and acetonitrile (CD₃CN, Fluorochem and Sigma Aldrich, NMR-grade), were added to some EPR and NMR samples to probe metal coordination to these species.

All solutions were prepared under argon and all salts were dried under dynamic vacuum at 100 or 110 $^{\circ}$ C.

EPR spectroscopy

Mixing, storage, and heat-treatment of electrolyte solutions was performed in Eppendorf tubes made from polypropylene, which is HF-resistant. Solutions were transferred into 2 mm outer diameter (O.D.) quartz EPR tubes (Wilmad, CFQ) for X-band, and 0.9 mm O.D. Suprasil tubes (Wilmad) for Q-band experiments. Tubes were sealed and transferred from the glovebox into the pre-cooled EPR resonator within 15 min after preparation. A Bruker ElexSys E580 spectrometer equipped with an EN4118X-MD4 resonator for X-band and an EN5107-D2 resonator for Q-band frequencies was used for experiments at a temperature of 20 K. Microwave amplification was performed with a 1 kW travelling-wave tube (TWT) pulse amplifier at X-band and with a 150 W TWT at Q-band; radiofrequency amplification was done with a 150 W amplifier.

Field-swept pulsed EPR spectra were obtained using the Hahn echo pulse sequence $\pi/2$ - τ - τ -echo and a two-step phase cycle. For X-band, $\tau=200$ ns and pulse durations $\tau_{\pi/2}=12$ ns and $\tau_{\pi}=24$ ns; for Q-band, $\tau=160$ ns and pulse durations $\tau_{\pi/2}=20$ ns and $\tau_{\pi}=40$ ns.

Hyperfine sublevel correlation⁸¹ (HYSCORE) spectra were recorded using the sequence $\pi/2-\tau-\pi/2-t_1-\pi-t_2-\pi/2-\tau$ -echo with $\tau=80$, 120 ns, $\tau_{\pi/2}=12$ ns, and $\tau_{\pi}=24$ ns. Multiple τ -values were used to remove blind spot artifacts and t_1 , t_2 were incremented by 20 ns starting from 80 ns. A four-step phase cycle was applied. Two-dimensional time traces were baseline-corrected with a third-order polynomial, apodised with a Hamming window function, and zero filled to 1024 points in each dimension, followed by 2D Fourier transformation and calculation of the absolute value. Davies-type electron nuclear double resonance (ENDOR) experiments were conducted at Q-band using the pulse sequence π -D- $\pi/2-\tau$ - π - τ -echo with $t_{\pi/2}=100$ ns, $t_{\pi}=200$ ns, and $\tau=450$ ns. During the delay D, an rf π -pulse lasting 10 μs was applied.

DFT calculations and EPR spectra simulation

Density functional calculations were conducted using ORCA 5.0.1.82 Structures were geometry optimised with the hybrid functional TPSSh, 83,84 the zeroth-order regular approximation (ZORA), 85,86 and def2-TZVP(-f) basis sets 87 in their ZORArecontracted version.88 Decontracted def2/J auxiliary basis sets were employed for the resolution-of-identity and chain-ofspheres approximation. The convergence criterion was set to tight self-consistent-field. Zero-field splitting and hyperfine coupling tensors were calculated using the hybrid functional PBE0⁸⁹ and ZORA. ZORA-def2-TZVP(-f) basis sets were modified through full s shell decontraction and addition of three steep Gaussians, as explained elsewhere. 90,91 Spin-orbit coupling was calculated using the spin-orbit mean-field approximation (SOMF(1X)).92 Integration accuracy was set to defgrid3 and radial accuracy IntAcc to 11 for manganese and 9 for all other atoms.

EPR spectra were simulated using EasySpin v6.0.0-dev.49^{93,94} running in Matlab v2021b (MathWorks). HYSCORE spectra were

simulated considering all magnetic nuclei with hyperfine tensors as obtained from DFT calculations using the simulation module saffron. Second-order perturbation theory and the product rule were used. Input parameters were set as used experimentally and electronic relaxation times as $T_{1\rm e}=80~\mu \rm s$ and $T_{2\rm e}=0.4~\mu \rm s$, which are in the range of those experimentally determined. Post-processing was equivalent as for experiments. $^1 \rm H$ powder Davies ENDOR spectra were simulated at Q-band frequencies assuming one coupled $^1 \rm H$ nucleus using the simulation module salt. The obtained spectra were multiplied with the Davies ENDOR detection function. 95,96

NMR spectroscopy

 1 H and 19 F NMR relaxation measurements of electrolyte solutions were performed at \sim 25 $^{\circ}$ C on a Bruker Avance III HD 300 MHz spectrometer using a Bruker double-channel MicWB40 probe. NMR spectra were collected on a Bruker Avance III HD 500 MHz spectrometer using a BBO probe, with a sealed capillary of C_6D_6 added to the NMR tube for field locking. No deuterated solvents were used for measurements at 300 MHz. Spin–lattice T_1 measurements were performed using the inversion recovery pulse sequence; spin–spin T_2 measurements were performed using the Carr–Purcell–Meiboom–Gill (CPMG) pulse sequence 97,98 with echo spacings of τ = 2 ms for most solutions. For 19 F measurements of Mn $^{2+}$ -containing solutions, echo spacings of 1 ms were used, due to faster relaxation. NMR tubes were filled in an argon glovebox and sealed with J-Young valves.

Coordination to lithium salts. The following salts were used to assess transition metal behaviour at the SEI: LiOH (Alfa Aesar, 99.995%), LiF (Sigma Aldrich, 99.995%), Li₃PO₄ (Sigma Aldrich), Li₂CO₃ (Alfa Aesar, 99.998%), Li₂O (Alfa Aesar, 99.5%), Li₂O₂ (Acros Organics, 95%), LiOMe (Sigma Aldrich, 98%), LiOEt (Sigma Aldrich, 95%), Li₂C₂O₄ (Alfa Aesar, 99+%), LiO-CHO (Alfa Aesar, 98%), LiOAc (Sigma Aldrich, 99.95%), Li(acac) (Sigma Aldrich, 97%). All salts were dried under vacuum at 100 °C before use. In plastic vials, 1 mL of 3:7 EC:EMC (v/v)-diamagnetic or containing 1 mM Mn(TFSI)2 or 1 mM Ni(TFSI)2—was added to 20 mg of each salt (10 mg for LiOMe, LiOEt, and Li₂O₂; 40 mg for LiF). Solutions were shaken twice per day; after two days, solutions were removed from the argon atmosphere and 150 µL of solution was pipetted off the top and added to 2.5% aqueous nitric acid. Samples were analysed for Li, Mn, and Ni concentration via ICP-OES.

ICP-OES analysis

ICP-OES measurements were performed on an iCAP 7400 Duo ICP-OES Analyzer in axial mode (Thermo Fisher Scientific). Calibration points were measured with multi-element standard solutions at concentrations of 0.005–20.0 ppm.

Results and discussion

EPR spectroscopy

The following sections contain results from pulsed EPR spectroscopy of frozen electrolytes performed at a temperature

of 20 K. Measurements were optimised for detecting ligand hyperfine couplings of $Mn(\pi)$ complexes, which exhibit sufficiently long electronic relaxation times for this technique.

Field-swept EPR spectra

Fig. 1 shows X-band Hahn-echo-detected pulsed EPR spectra of frozen 1 M LiPF₆ in 3:7 EC: EMC (LP57) electrolyte containing 8 mM Mn²⁺. The freshly prepared sample (lower spectrum) exhibits six central transition resonances corresponding to hyperfine coupling to the six nuclear spin states of the I = 5/2nucleus 55Mn. The additional features associated with each of these peaks arise from a rhombic zero-field splitting interaction, which characterises the symmetry of the complex. This spectrum was assigned in our previous work to a sixfold coordinated Mn(II) complex coordinated by the oxygen atoms of the carbonyl functionalities from mainly EC, and minorly EMC, with PF₆⁻ located in the second solvation shell. When the identical sample is stored at 35 °C for 24 h, representing a mild heating protocol, the distinct six central transitions are less pronounced and the very broad outer transitions at around 300 and 400 mT are seen more clearly (middle spectrum). An analysis of the degraded electrolyte using 19F solution NMR revealed the presence of PO₂F₂⁻ and/or HPO₂F₂ species at a concentration of approximately 9 mM. To explore the effect of the PO₂F₂⁻ anion further, frozen electrolytes with LiPO₂F₂ salt added in a Mn²⁺:PO₂F₂ ratio of either 1:2 or 1:10 (corresponding to 16 and 80 mM LiPO₂F₂ solutions) were

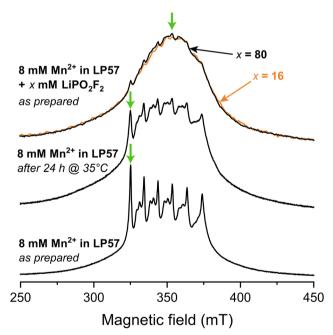


Fig. 1 Field-swept echo-detected X-band pulsed EPR spectra, recorded at 20 K. Frozen samples of 8 mM Mn(TFSI) $_2$ dissolved in 1 M LiPF $_6$ in 3:7 EC:EMC (LP57) are investigated freshly prepared (bottom), after heating at 35 °C (middle), and with 16 mM (orange) or 80 mM (black) LiPO $_2$ F $_2$ added (top). Orange and black arrows (top) point at the partially overlapping spectra for samples with 16 and 80 mM LiPO $_2$ F $_2$ addition, respectively. Green arrows show the magnetic fields used for the hyperfine spectroscopy experiments (Fig. 2).

Paper

prepared. These now exhibit almost featureless pulsed EPR spectra, where the sharp central transitions are barely visible. Despite the different Mn^{2+} : $PO_2F_2^-$ ratios, both samples give rise to almost identical spectra.

The increasing intensity away from the sharp central transitions and line broadening observed for the mildly heated and LiPO₂F₂-containing samples indicate contributions from complexes exhibiting either a large zero-field splitting, a large distribution of zero-field splitting constants, and/or strain effects. 99-101 To estimate the relative sizes of these interactions, the zero-field splitting interactions of sixfold coordinated Mn(II) complexes containing carbonate and fluorophosphate ligands in the first coordination shells were investigated by DFT. The zero-field splitting magnitude follows the series: carbonate (6 EC) < 6 $HPO_2F_2/6$ $PO_2F_2^ \ll$ mixed $PO_2F_2^-/HPO_2F_2 \approx$ mixed carbonate/PO₂F₂ ligands (SI, Fig. S1). Sixfold PO₂F₂ coordination is, however, considered unlikely due to an overall complex charge of −4. HPO₂F₂ was investigated because a trace amount of water may react with LiPF₆ under mildly elevated temperature to form HPO₂F₂, a species which is only weakly acidic.102 Although the calculated absolute values of zero-field splitting constants are often unreliable, 101 the increase in zero field splitting for complexes containing $PO_2F_2^-/HPO_2F_2$ in the Mn^{2+} coordination shell could explain the increase in broadening from the pristine sample to the mild heat-treated and $LiPO_2F_2$ -additive samples. To further investigate the coordination to Mn^{2+} , hyperfine-targeted pulsed EPR measurements were applied to investigate the hyperfine interactions with the various NMR active nuclei.

X-band hyperfine sublevel correlation (HYSCORE) spectroscopy

The above-introduced samples of Mn(II) in 1 M LiPF₆/3:7 EC:EMC (LP57), either freshly prepared, mildly heat-treated, or with added LiPO₂F₂, were first analysed by HYSCORE spectroscopy (Fig. 2, upper row). This four-pulse, two-dimensional EPR experiment is performed at a constant magnetic field (*i.e.*, at one particular position in the EPR spectrum, as marked in Fig. 1 with green arrows) and detects coupling to magnetic nuclei in the solvation sphere(s) of the Mn(II) ion, with the nuclear transitions $\nu_{\alpha,\beta}$ (for S=1/2) being observed, to first order, at frequencies

$$\nu_{\alpha,\beta} = \nu_{\rm I} \pm A/2$$
 if $|A/2| < \nu_{\rm I}$

centred at the nuclear Larmor frequency $\nu_{\rm I}$ with hyperfine coupling constant A. Possible nuclei are 1 H from EC and

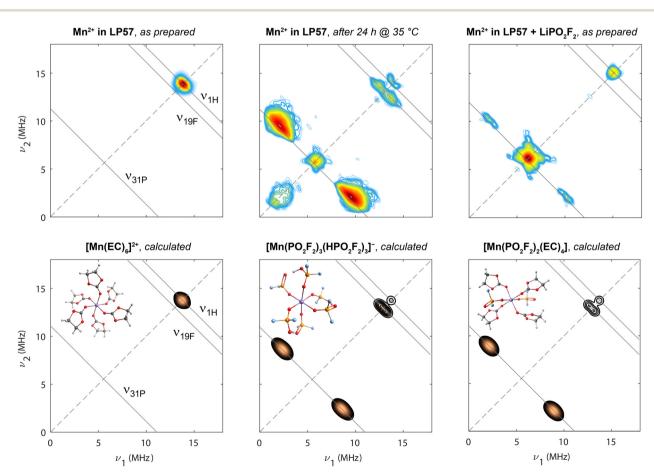


Fig. 2 Experimental (upper row) and calculated (lower row) HYSCORE spectra at 9.8 GHz (X-band; 20 K). Spectra from samples containing 8 mM Mn(TFSI)₂ dissolved in 1 M LiPF₆ in 3:7 EC:EMC (left), with mild heat-treatment at 35 °C for 24 h (centre), and addition of 80 mM LiPO₂F₂ (right) are shown. Experiments were conducted at the magnetic field positions indicated by green arrows in Fig. 1. The diagonal is shown with a dashed line. Anti-diagonal (solid) lines are shown at relevant nuclear Larmor frequencies. Calculations are shown for three clusters, $[Mn(EC)_6]^{2+}$, $[Mn(PO_2F_2)_3]^-$ and $[Mn(PO_2F_2)_2(EC)_4]$.

EMC as well as 6,7 Li, 19 F, and 31 P from the electrolyte salt LiPF₆, while 13 C and 17 O are not sensitive enough due to their low natural abundance. Nuclei in impurities or degradation products may also need to be considered if these species become ligands. The time-domain detection allows these magnetic nuclei, with their respective hyperfine coupling, to be probed simultaneously, and the two-dimensionality increases resolution since, first, nuclear frequencies are spread along the diagonal and, second, the splitting between peaks on the anti-diagonal corresponds to the hyperfine coupling constant A. The spectrum of the pristine sample solely exhibits an intense signal on the diagonal at the nuclear Larmor frequency $\nu_{^{1}\text{H}}$, indicating weakly coupled and thus remote ^{1}H nuclei. This is in line with proposed carbonate coordination with Mn–H distances of ≥ 5.5 Å. 11

After mild heating of the Mn(II)-containing sample, the resonance at ν_{1H} splits, indicating a larger ¹H hyperfine interaction, and new resonances centred at $\nu_{^{31}P}$ and $\nu_{^{19}F}$ appear, indicating a change of the Mn²⁺ coordination shell. The most intense signals cluster around the 31P anti-diagonal with hyperfine coupling constants of around A = 5.5-10 MHz. While the intensity of HYSCORE signals is determined by the number of coupled nuclei, the coordination number is difficult to directly determine, as the signal intensifies when A/2 approaches $\nu_{\rm I}$ ($\nu_{\rm ^{31}P}$ = 5.6 MHz) and is also affected by experimental parameters. The separate $\nu_{^{31}P}$ signal on the diagonal indicates additional, more remote 31P-containing species in outer solvation spheres with weaker but non-zero hyperfine coupling constants. Coupling parameters of $A(^{19}F) = 1.3 \text{ MHz}$ and $A(^{1}H) = 0.6$ MHz are extracted from the observed maximum antidiagonal intensity at the respective Larmor frequencies. The HYSCORE signals exhibit a specific curvature, which is pronounced for ¹H and to some degree for ³¹P and ¹⁹F: generally, the further away resonances are from the diagonal, the more these resonances move away from the anti-diagonal toward higher frequencies, as discussed in more detail in ref. 103. This line shape results from a continuous variation of hyperfine tensor values due to a conformational distribution rather than exactly defined atomic positions in the frozen state, 91,103,104 which is also consistent with the observed line broadening in Fig. 1. The shift away from the nuclear Larmor frequency towards higher frequency directly on the diagonal, as best seen for ³¹P but also to some degree for ¹H, is indicative of the dipolar contribution to the hyperfine interaction.¹⁰⁵ The signal at low $\nu_{1,2}$ results from imperfect microwave pulses and limited excitation bandwidth.

For the sample with added LiPO₂F₂, only signals due to coupling to ^{31}P and ^{1}H are resolved. A doublet on the $\nu_{^{31}P}$ antidiagonal from strongly coupled ^{31}P spins is detected at identical frequencies as observed for the mildly heated sample; however, it is far less intense. In contrast, the intensity maximum is found on the diagonal, the signal arising from a large number of weakly interacting and thus more remote ^{31}P spins. The ^{1}H signal is also located on the diagonal and is not as clearly split as for the mildly heated sample, again indicating more remote ^{1}H nuclei.

DFT calculations of $A_{x,y,z}$ and subsequent spectra simulation (Fig. 2, lower row) allow a variety of structural models to be compared to the experimental data. For the pristine sample, a simulated HYSCORE spectrum of a Mn(II) complex sixfold coordinated by EC provides a good match to the experiment. The broadening of the diagonal peak, seen in the spectral simulations and assigned to weak coupling to nearby ¹H spins, arises from both the broadening due to T_{2e} relaxation, with the values used in this simulation specified in the Methods section, and the slightly varying hyperfine tensors for all 24 involved weakly coupled ¹H nuclei. In the experiment, nuclei from outer solvation shells and conformational differences between complexes also contribute to the broadening, which are both disregarded in all simulations. Mn(II) complexes with sixfold coordination containing either both fluorophosphate and EC ligands, or both HPO₂F₂ and EC ligands resemble the experimental spectrum of the mildly heat-treated sample, consistent with complexes proposed above. Other structure models, including bidentate oxygen coordination of PO₂F₂-, or PF₆coordination as a source for 31P and 19F couplings, are precluded, since they lead to hyperfine coupling values or simulated HYSCORE features that are not consistent with the experimental spectra as, for example, the coupling to the ³¹P spins is too weak (Fig. S2). The underlying ratio of protic HPO₂F₂ to aprotic PO₂F₂⁻ is not extractable, because the effect of protonation on the simulated spectrum is minor (Fig. S2). The weaker peak seen on the diagonal near the ³¹P frequency in the experimental spectrum is assigned to P-containing complexes that are in more distant (outer sphere) coordination shells: all P-containing ligands—even PF₆—in the first coordination shell give rise to pronounced ³¹P hyperfine coupling.

DFT seems to underestimate hyperfine coupling strengths, particularly for 19F and 1H, as also observed for predicted 55Mn coupling tensors (Table S1). As discussed previously, 106,107 d5 systems still prove particularly challenging for DFT due to the large electron-electron exchange and correlation interactions, also manifested in DFT functional sensitivity (Fig. S1 and S2). Apart from DFT errors, the optimised lowest-energy structures also likely deviate significantly from the experimental situation. The proposed Mn(II) fluorophosphate structures, and in particular the lowest-energy location of the proton in the HPO₂F₂ ligands, depend on the HPO₂F₂: PO₂F₂ ratio (Fig. S3). Whereas in [Mn(HPO₂F₂)₆]²⁺, all -OH groups face away from the center of the complex, with Mn-H distances of 5.0-5.5 Å, inter-ligand hydrogen bonds are formed in [Mn(PO₂F₂)₃(HPO₂F₂)₃]⁻, resulting in [-Mn-O-P-O-H-O-P-O-] rings with shorter Mn-H distances of ~3.9 Å. Hydrogen bonding via smaller rings, e.g. [-Mn-O-P-O-H-O-], is also conceivable. Additionally, outer solvation shells might affect bond lengths, angles, and dihedrals, which have a large effect on all hyperfine coupling tensors of the complex, 91,103 which might explain deviations between experimental and simulated spectra.

Considering the sample with LiPO₂F₂, the experimental spectrum is noticeably different from the mildly heated electrolyte sample's HYSCORE spectrum and does not reflect pure inner sphere fluorophosphate coordination. Assuming a lack of

protic HPO₂F₂ in this solution and charge neutrality, the first structural model considered was a [Mn(PO₂F₂)₂(EC)₄] complex. The reduced symmetry and therefore larger zero-field splitting (Fig. S1) could explain the broad field-swept EPR spectrum (Fig. 1). Although the intensity contribution of ¹H resonances increases relative to complexes with no EC molecules, agreement with the experimental HYSCORE spectrum is still poor. Nonetheless, this and related complexes are still likely responsible for the weak signals along the 31P anti-diagonal, with associated couplings to 19F and 1H too weak to be resolved. The intense ³¹P resonance near the diagonal indicates the presence of a superimposed second complex type, the stronger ¹H diagonal peak than seen for the degraded electrolyte suggesting that more EC ligands are present in the Mn²⁺ coordination shell. In contrast to the mildly heated sample, fluorophosphate is present as unprotonated PO₂F₂⁻. A preference of PO₂F₂⁻ for Li⁺ might hinder Mn²⁺ coordination, placing it in outer solvation shells of Mn²⁺ resulting in an intense ³¹P signal on the diagonal, indicating weaker hyperfine interactions. The underlying Mn(II) carbonate complex would account for the ¹H diagonal signal. Additional experiments show that the relative ratio of strongly to weakly coupled ³¹P increases with the LiPO₂F₂: Mn²⁺ ratio (Fig. S4, ratio ranging from 2:1 to 10:1). This indicates that PO₂F₂⁻ is more likely to move from an outer to the inner solvation shell with increasing PO₂F₂ concentration, following the law of mass action.

Another possible explanation of the HYSCORE spectra involves the formation of Mn(II) complexes containing side products as ligands. A number of (oligo-)organo-(fluoro)phosphates can form through PO2F2- reaction with EC or EMC, 108,109 which could bind to Mn2+ via carbonate fragments that are chemically bonded to phosphate(s), accounting for the HYSCORE 31P and 1H signals. However, we consider such

degradation products unlikely because significant amounts only form above 40 °C, 110 and the 19F NMR spectra of these samples showed that the dominant degradation product is PO₂F₂⁻/HPO₂F₂.

Q-band ENDOR

To support the assumption that trace moisture is responsible for HPO₂F₂ formation in the mildly heated sample. Davies-type electron nuclear double resonance (ENDOR) spectroscopy at Q-band was performed. In an ENDOR experiment, radiofrequency irradiation $\nu_{\rm rf}$ drives nuclear transitions and, thus, modifies the evolution of magnetization under the (isotropic and anisotropic) hyperfine interaction, altering the electron spin echo intensity. This experiment often allows the principal components of the hyperfine tensor $A_{x,y,z}$ to be extracted, unlike in a HYSCORE experiment, where the modulation amplitude tends to vanish for orientations aligned with the principal axes. Here, the method is used to compare the 19F-Mn²⁺ and ¹H-Mn²⁺ hyperfine interactions in multiple electrolytes, including electrolytes containing either LiPF6 or LiTFSI salts, before and after heating and with added water (Fig. 3). Their corresponding 1D field-swept EPR spectra are displayed in Fig. S5. The pristine LiPF₆ electrolyte sample exhibits an intense ENDOR signal at around $\nu_{^{1}\text{H}}$ (50.45 MHz) assigned to carbonates, and a low-intensity signal around $\nu_{^{19}\mathrm{F}}$ assigned to PF₆ in outer solvation shells (Fig. 3, left panel, bottom spectrum).¹¹ After mild heating (24 h at 35 °C), the hyperfine coupling to both 19F and 1H is larger; the signals centred around $\nu_{^{19}\text{F}}$ become more intense, with the more distinct features indicating better defined complexes. Since fluorophosphates result from LiPF₆ decomposition, pristine and heated (24 h at 45 °C) samples were also prepared in a LiTFSI-based,

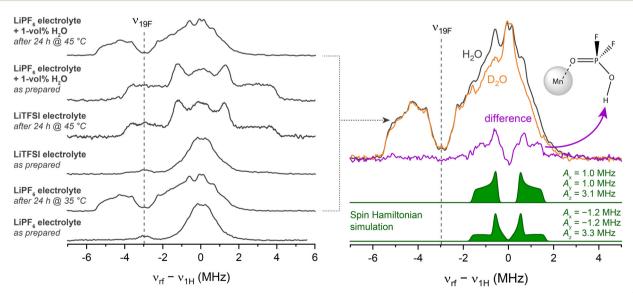


Fig. 3 Davies-type electron nuclear double resonance (ENDOR) spectra recorded at 34 GHz (Q-band) of a series of samples containing 8 mM Mn²⁺ in a 3:7 EC: EMC solvent with 1 M Li salt (LiPF₆ and LiTFSI) as indicated (left). The radiofrequency axis is shifted to yield the ¹H Larmor frequency at 0 MHz. Right: ENDOR spectra of the LiPF₆-containing electrolyte with either 1 vol% H₂O (black) or D₂O (orange). Spin Hamiltonian fits to these spectra (green) were adjusted to reproduce the difference spectrum (purple). The complex shown, Mn(HPO₂F₂), was used to simulate the spectra, with simulations for two different axial hyperfine tensors being shown.

but otherwise identical, electrolyte for comparison. The spectrum of the pristine LiTFSI electrolyte resembles that of the LiPF₆ electrolyte. After heating, however, a very different ligand environment is detected, with couplings (predominantly from ¹H) that are in very good agreement with the spectral fingerprint of [Mn(OH₂)₆]²⁺. 112,113 Water has clearly been formed, either as part of an electrolyte degradation reaction or because it has entered into the NMR tube during the heating step. When 1 vol% (0.56 M) H₂O was intentionally added to the LiPF₆ electrolyte pristine sample, a very similar spectrum to that seen for the LiTFSI heated sample, i.e., [Mn(OH₂)₆]²⁺, is observed. However, after heating this sample for 24 h at 45 °C, the spectrum (Fig. 3, top right) is essentially identical to that of the mildly heated sample without water addition, indicating that fluorophosphate has formed, and suggesting that fluorophosphate coordination is preferred over H₂O coordination.

The ENDOR spectrum of this mildly heated (wet) LiPF₆ electrolyte sample contains multiple overlapping hyperfine coupling patterns, possibly from more than one species. To reduce complexity, D2O instead of H2O was added to the solution so as to form DPO₂F₂ via

$$LiPF_6 + 2D_2O \rightarrow DPO_2F_2 + 3DF + LiF$$
 (1)

Contributions from deuterium are shifted away to a different frequency regime in the ENDOR spectrum because ν_{2n} is 6.5 times smaller than ν_{1} . The difference between the spectra of the H₂O and D₂O-containing electrolytes reduces to a simple ¹H coupling pattern, which exhibits a distinctly different spectral fingerprint from that of water ligands (Fig. 3, right panel). The coupling pattern is characteristic of an axially symmetric hyperfine coupling tensor $(A_x = A_y \neq A_z)$, which indicates a single or multiple, but magnetically very similar, ¹H position(s). Assuming a single contributing ¹H nucleus, two sets of hyperfine coupling constants are conceivable due to sign ambiguities: (1.0, 1.0, 3.1) or (-1.2, -1.2, 3.3)in MHz. The anisotropic part can be directly derived from these principal components, and used to estimate the electronnuclear distance by assuming point-dipoles. This approximation is inaccurate for a transition metal complex with delocalised spin density (Fig. S3), but may serve as method for extracting a rough orientation of the complex. The two sets of hyperfine coupling constants imply Mn-H distances of 4.8 and 3.7 Å, respectively, lying in the range of DFT optimised distances of 3.9-5.5 Å. The residual resonances centred around $\nu_{^{1}\mathrm{H}}$ are from non-water sources and correspond to comparably low coupling strengths with $A \approx 0.2$ MHz; these are assigned to outer solvation shells and/or remaining carbonate ligands in the first solvation shell. For resonances centred at $\nu_{^{19}\rm F}$, three characteristic features can be extracted, which are seen more clearly at lower frequencies compared to $\nu_{^{19}\mathrm{F}}$ since there is no overlap with the resonances associated with ¹H. The lowestfrequency rising edge at $\nu_{\rm rf}$ – $\nu_{^1{\rm H}}$ \approx –5.4 corresponds to A \approx 4.7 MHz, the local maximum to 2.8 MHz, and the falling edge to 1.3 MHz. The unknown number of contributing nuclei and the unknown tensor symmetry impedes further analysis, but do indicate that an inner sphere complex, with large ¹⁹F hyperfine interactions, is present. Additional EPR studies using deuterated additives were performed to explore their ability to displace carbonate/fluorophosphate ligands from the Mn²⁺ solvation shell (Fig. S6). Results indicate that displacement from the first coordination sphere is attained with CD₃OD, partially with d₆-DMSO, and to some degree with CD₃CN.

NMR spectroscopy

The paramagnetic relaxation theory underpinning this section can be found in our previous work,11 and in many other reviews;¹¹⁴ a condensed version is also presented in the SI.

NMR relaxometry of degraded electrolyte solutions

To understand how coordination may change between pristine and degraded electrolyte solutions, pristine solutions were heated at 60 °C for five days and the spin lattice R_1 (= $1/T_1$) relaxation rates were measured daily. Relaxation rates of 1 M LiPF₆ in 3:7 EC:EMC electrolyte solutions containing either 1 mM Mn(TFSI)₂ or 1 mM Ni(TFSI)₂ are presented in Fig. 4 as paramagnetic relaxation rates (R_{1p}) . Values were calculated by subtracting the relaxation rates R_{1d} of pristine diamagnetic electrolyte solutions from the measured relaxation rates, R_{1p} = $R_1 - R_{1d}$, ⁶² where R_{1d} for 1 M LiPF₆ in 3:7 EC:EMC v/v is 0.6307 $\pm 0.0002 \text{ s}^{-1}$ for ¹H of EC and $0.352 \pm 0.003 \text{ s}^{-1}$ for ¹⁹F of PF₆, as determined in our previous work. 115 This method assumes that the R_{1d} relaxation rates of pristine solutions remain constant over a period of heating, or with the addition of a small amount of contaminant. We suggest that minor compositional changes to the electrolyte should not significantly affect bulk properties such as viscosity, and that the concentration of degradation species is small relative to the other solution components: 1 M LiPF₆, 4.5 M EC, and 6.8 M EMC.

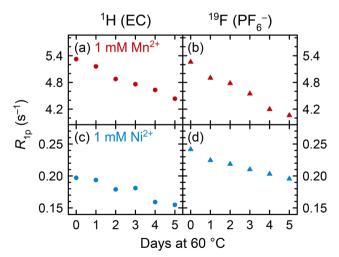


Fig. 4 (a) and (c) ¹H EC (circles) and (b) and (d) ¹⁹F PF₆⁻ (triangles) longitudinal paramagnetic relaxation rates (R_{1p}) of Mn^{2+} - or Ni^{2+} containing electrolyte solutions across five days of heating at 60 °C. Electrolyte solutions comprised 1 M LiPF₆ in 3:7 EC:EMC (v/v) with 1 mM Mn(TFSI)₂ (red) or Ni(TFSI)₂ (blue). Solutions were cooled to ambient temperature (~25 °C) before relaxation rates were measured.

In both Mn²⁺- and Ni²⁺-containing electrolyte solutions, the ¹H (EC) and ¹⁹F (PF₆⁻) R_{1D} values show a clear decrease across the heating period. With no substantial change in the total concentration of solution components, the decrease in R_{1n} values indicates a decrease in the number of EC or PF₆ molecules in the transition metal solvation shells. This suggests that the transition metal ions must be preferentially coordinating to a new component in the degraded electrolyte. (Electrolyte degradation species were not observable in these samples owing to both the paramagnetic ions and the use of a solid-state spectrometer for these measurements; however, later NMR experiments with heated diamagnetic electrolyte showed PO₂F₂ and HF as the major degradation species (Fig. 7), which is also consistent with analysis of heated EPR samples.) While the lifetimes of the different Mn²⁺/Ni²⁺ complexes may change, affecting NMR relaxation times, 11 the EPR results in the previous section clearly indicate changes in the

nature of the complexes present in the degraded electrolyte, consistent with the NMR results shown here.

Transition metal coordination to PO₂F₂

To isolate the effect of $PO_2F_2^-$ on transition metal coordination, $LiPO_2F_2$ was directly added to pristine electrolyte solutions. Fig. 5a shows NMR spectra for 1 M LiPF₆ in 3:7 EC:EMC (v/v) containing added LiPO₂F₂, Mn^{2+} , or both; Fig. 5b shows relaxation measurements for solutions containing 1 mM Mn^{2+} or Ni^{2+} and 0–50 mM LiPO₂F₂.

As expected, the 19 F NMR spectrum of the diamagnetic solution containing LiPO₂F₂ (Fig. 5a, black line) shows narrow doublets for both PF₆⁻ and PO₂F₂⁻, while the solution that contains Mn²⁺ but not LiPO₂F₂ (red line) shows a broadened PF₆⁻ doublet only. However, in the solution containing both Mn²⁺ and LiPO₂F₂ (purple line), the PF₆⁻ doublet is much narrower than its counterpart in the Mn²⁺-only solution; additionally, the

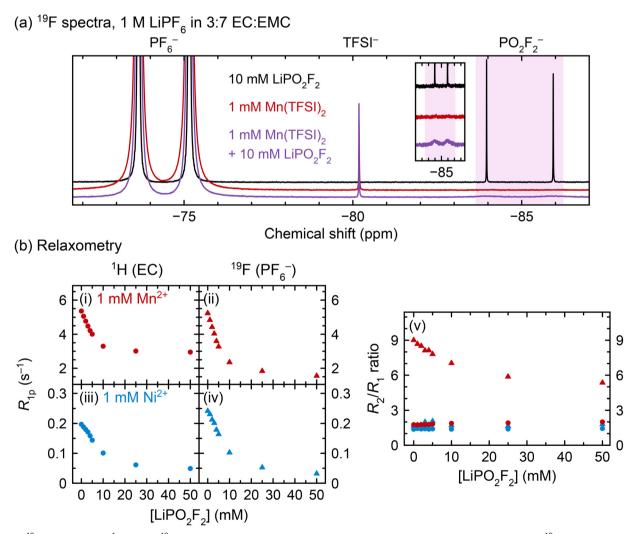


Fig. 5 (a) 19 F spectra and (b) 1 H EC and 19 F PF $_{6}^{-}$ relaxation data of pristine electrolyte solutions to which LiPO $_{2}$ F $_{2}$ was added. 19 F spectra are shown for solutions containing LiPO $_{2}$ F $_{2}$, Mn $^{2+}$, or both; inset shows enlargement of the PO $_{2}$ F $_{2}^{-}$ resonance. Longitudinal paramagnetic relaxation rates (R_{1p}) and R_{2} / R_{1} ratios are shown for the 1 H EC (circles) and 19 F PF $_{6}^{-}$ resonances (triangles), in solutions containing Mn $^{2+}$ (red) or Ni $^{2+}$ (blue). Electrolyte solutions comprised 1 M LiPF $_{6}$ in 3 : 7 EC : EMC (v/v).

 $PO_2F_2^-$ doublet is severely broadened relative to the $PO_2F_2^-$ doublet in the diamagnetic solution, indicating faster relaxation. The same behaviour can be seen in Fig. 5b, panel (ii), where the ^{19}F $PF_6^ R_{1p}$ values decrease in Mn^{2+} -containing solutions as $LiPO_2F_2$ is added.

In Fig. 5b, panels (i-iv), the 1 H (EC) and 19 F (PF $_{6}$) R_{1p} values decrease with increasing LiPO₂F₂ concentration. ¹H EMC relaxation rates also decrease (not shown). The diamagnetic relaxation rates should not be affected in these samples as the solution viscosity increase due to the addition of 0-50 mM LiPO₂F₂ is likely minor. Regardless, a viscosity increase would lead to an increase rather than a decrease in relaxation rates, as the solutions are in the fast motion regime. 11 The decrease in R_{1p} values is consistent with the results in Fig. 4, where EC and PF₆ relaxation rates slowed as PO₂F₂ and other fluorophosphates were generated in situ by heating. The decrease in R_{1p} values in Fig. 5b begins to level off at ~10-25 mM LiPO₂F₂ addition, indicating a very strong competition for Ni²⁺/Mn²⁺-PO₂F₂⁻ complexation over Ni²⁺/Mn²⁺-PF₆⁻ interactions/complexes. The larger decrease in 19 F R_{1p} rates over the 1 H values suggests that EC is still involved in binding to Ni²⁺/Mn²⁺ even in the presence of PO2F2-, which is consistent with the EPR results.

Fig. 5b, panel (v) shows the R_2/R_1 ratios for the same solutions studied in panels (i)-(iv). The only instance where the R_2/R_1 ratio exceeds 2 is the $^{19}{
m F}$ ${
m PF_6}^-$ relaxation in ${
m Mn}^{2+}$ containing solutions (red triangles), where the R_2/R_1 ratio decreases from 9.0 to 5.4 as 50 mM LiPO₂F₂ is added. This indicates that a different relaxation mechanism is driving the R_2 rates in this system. As discussed in our previous paper, ¹¹ and explored further in the SI, one potential source of an R_2/R_1 ratio greater than one is a contribution of the contact (throughbond) relaxation mechanism to R_2 , while the major source of R_1 relaxation originates from a dipolar (though-space) interaction. Thus, an R_2/R_1 ratio of $\gg 1$ could be ascribed to a short-lived inner sphere complex. Since the hyperfine interaction for a Mn²⁺-PF₆⁻ inner sphere complex should remain the same with added LiPO₂F₂, the convergence of R_2 towards R_1 could then be ascribed to a decrease in the relative fraction of inner sphere νs . outer sphere Mn²⁺-PF₆⁻ complexes. However, the HYSCORE EPR spectrum shows no evidence of an inner sphere complex—i.e., no strong ¹⁹F/³¹P-Mn²⁺ hyperfine interaction is seen, while the ENDOR spectrum of the same sample reveals only a weak interaction likely due to an anisotropic (dipolar, throughspace) interaction, indicating the presence of some PF₆⁻ anions in the outer coordination shells in the frozen electrolytes. Thus, the time that a PF₆⁻ anion spends on average in an inner sphere complex must be extremely short, so that it is not captured in the frozen solution. It is also possible that a second relaxation mechanism involving a change in the dynamics of exchange in and out of the outer sphere coordination shell may contribute to some of the observed changes in the relaxation processes, but to test this proposal is beyond the scope of this work.

While it could be argued that the $PO_2F_2^-$ addition slowed the 1H and ^{19}F relaxation rates by causing Mn^{2+} precipitation, it

has been shown that LiPO $_2$ F $_2$ does not cause transition metal precipitation in battery electrolytes. Two experiments in this work also suggest that precipitation does not occur: (i) when a solution of 1 mM Mn $^{2+}$ in 3:7 EC:EMC was saturated with LiPO $_2$ F $_2$, ICP-OES measurement revealed that the Mn concentration in solution was unchanged; (ii) the NMR spectra in Fig. 5a show that when 10 mM LiPO $_2$ F $_2$ is added to a solution of 1 M LiPF $_6$ in 3:7 EC:EMC + 1 mM Mn $^{2+}$, the PO $_2$ F $_2$ resonance becomes extremely broad, but does not disappear, indicating that it is interacting with Mn $^{2+}$ but is still present in solution. Notably, the result of transition metal coordination to PO $_2$ F $_2$ in solution, shown by both EPR and NMR, may also apply to other cell chemistries, as PF $_6$ salts are used in beyond-lithium systems, including sodium-ion, potassium-ion, and calcium-ion cells. 116

Transition metal coordination to other model degradation species

We now explore Mn²⁺ and Ni²⁺ coordination to two other degradation species, ethylene glycol (EG) and acetylacetonate (acac⁻) (Fig. 6). The solubility of Li(acac) in the electrolyte solution was found to be very small, so data are presented here for solutions that are saturated with Li(acac), roughly estimated to occur at ~ 5 mM Li(acac). Fig. 6a shows that after ethylene glycol addition to Mn²⁺- or Ni²⁺-containing solution, the ¹H (EC) R_{1p} values decrease, suggesting that ethylene glycol replaces (at least some) EC in the Mn²⁺ and Ni²⁺ solvation shells. Interestingly, instead of the ¹⁹F PF₆⁻ R_{1p} values decreasing, as occurs upon $LiPO_2F_2$ addition, the R_{1p} values increase. This suggests that PF_6 is in closer proximity to Mn2+ or Ni2+ when ethylene glycol is present. It is not likely that the fraction of coordinated PF₆increases, because EC coordination is preferred over PF₆ coordination and so the displacement of EC by an even more preferred coordination agent should not then facilitate additional PF6 binding.

Concurrently, the 1 H (EC) R_{2}/R_{1} ratio remains constant and the 19 F (PF₆ $^{-}$) R_{2}/R_{1} ratio decreases in Mn²⁺-containing

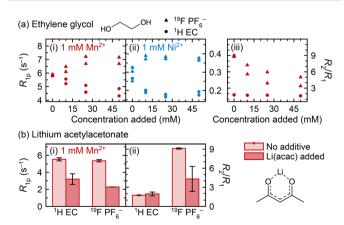


Fig. 6 Relaxation behaviour upon either (a) ethylene glycol or (b) Li(acac) addition to paramagnetic electrolyte solutions. $R_{\rm 1p}$ values and $R_{\rm 2}/R_{\rm 1}$ ratios are shown for $^{19}{\rm F}$ PF₆ $^-$ resonances (triangles) and $^{1}{\rm H}$ EC resonances (circles) in electrolyte solutions containing 1 mM Mn(TFSI)₂ (red) or Ni(TFSI)₂ (blue). The electrolyte solution comprises 1 M LiPF₆ in 3:7 FC:FMC ($_{\rm V}/_{\rm V}$)

solutions. It is noted here that the absolute value of R_2 decreases, not just the R_2/R_1 ratio—if the R_2/R_1 decrease were caused by R_2 remaining constant as R_1 increased, then R_2 would only decrease by 11-18%, not 43-63% as is observed. Together, the longitudinal and transverse relaxation behaviour is consistent with the interpretation of an inner solvation shell mostly composed of EC, which is displaced by ethylene glycol: the smaller size of ethylene glycol compared to EC results in a smaller first solvation shell, resulting in a closer approach by PF₆⁻ ions in the second solvation shell to Mn²⁺ or Ni²⁺, along, potentially, with different dynamics for PF₆⁻ exchange, and an increase in R_1 and decrease in R_2 . It is possible that EG binding reduces the albeit small probability that PF₆⁻ forms an inner sphere complex, also reducing the R_2/R_1 ratio.

We have previously suggested coordination to the ethylene glycol dianion for vanadyl ions dissolved in degraded LiPF₆ electrolyte solutions, supported by pulsed EPR measurements.⁷⁰ We note that the experiments in Fig. 6a used neutral ethylene glycol, but it is possible that if it exists in situ as the dianion, then the transition metal charge would be satisfied by the anionic ethylene glycolate, and coordination to PF₆⁻ may become significantly less favoured. The acidity of the electrolyte solution likely helps determine the favourability of transition metal coordination by determining whether potential coordinating ligands are neutral or charged.

The addition of Li(acac) to Mn²⁺-containing electrolyte (Fig. 6b) causes similar results as addition of LiPO₂F₂ (Fig. 5b), where the ${}^{1}H$ (EC) and ${}^{19}F$ (PF₆ $^{-}$) R_{1p} values both decrease and the ¹⁹F (PF₆⁻) R₂/R₁ ratio also decreases, suggesting both EC and PF₆⁻ are displaced from the inner and outer spheres. Notably, the ICP-OES results that will be discussed later show that Li(acac) causes precipitation of $\sim 9\%$ of 1 mM Mn²⁺ in 3:7 EC: EMC, which may have contributed to the observed decrease in R_{1p} values. Still, the qualitative interpretation of the NMR data here and the conclusion that acac affects the Mn²⁺ solvation shell is reasonable, because the dramatic change in the 19 F (PF $_6$ ⁻) R_2/R_1 ratio shows that the results in Fig. 6b are not only due to loss of overall Mn2+ in solution. Had a small amount of Mn2+ simply precipitated, and the overall concentration of Mn2+ were slightly smaller, the 19 F (PF₆⁻) R_2/R_1 ratio would not be expected to change significantly.

Electrolyte degradation induced by dissolved transition metals

Previous work has asserted that dissolved Mn2+ can itself induce PF₆⁻ degradation.^{8,14} This is now explored in work presented in Fig. 7, which shows the ¹⁹F (PF₆⁻) and ¹H (EC) relaxation rates, as well as the measured concentrations of PO₂F₂⁻ and HF generated, in solutions of 0.1 mM and 1.0 mM Mn²⁺. In one group of samples, Mn²⁺ was added before heating at 60 °C for ten weeks, and in the other group, Mn²⁺ was added after heating; if the Mn²⁺ ions were inert, results should be identical. NMR of the heated diamagnetic sample prior to any Mn²⁺ addition indicated that PO₂F₂⁻ and HF were the major degradation species. Mn concentrations were confirmed with ICP-OES and are indicated in parentheses in Fig. 7a; we note that duplicate samples were prepared from separate stock solutions of Mn²⁺,

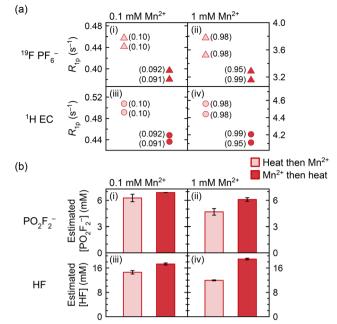


Fig. 7 (a) ¹⁹F PF₆⁻ (triangles) and ¹H EC (circles) longitudinal paramagnetic relaxation rates (R_{1p}) and (b) estimated concentrations of PO₂F₂⁻ and HF in electrolyte solutions to which Mn²⁺ was added before (red) or after heating (pink) at 60 °C for ten weeks. Values next to the relaxation data indicate the Mn concentration in mM measured by ICP-OES. PO₂F₂⁻ estimated concentrations were derived from integrating ¹⁹F spectra relative to PF₆ (assuming 1 M PF₆⁻); HF estimated concentrated were derived from ¹⁹F spectra as well as from ¹H spectra relative to EC (assuming 4.5 M EC). Electrolyte solutions comprised 1 M LiPF₆ in 3:7 EC:EMC (v/v), to which 0.1 or 1.0 mM Mn(TFSI)2 was added.

accounting for the small variation in Mn concentrations between some duplicates.

Since the generation of fluorophosphate degradation species results in reduced PF₆⁻ and EC relaxation rates, as the fluorophosphates compete for the Mn²⁺ ions (Fig. 4 and 5), the relaxation rates may be used as a proxy to monitor the degree of degradation in electrolyte solutions with the same Mn2+ concentration. In Fig. 7a, ¹H (EC) and ¹⁹F (PF₆⁻) longitudinal paramagnetic relaxation rates are slower in all samples that were heated in the presence of Mn²⁺, compared to samples where Mn²⁺ was added after heating. However, ICP-OES also showed a small but significant difference in the concentration of the nominally 0.1 mM samples, where the samples with Mn²⁺ addition before heating contained 0.1 mM Mn but the samples with Mn2+ addition after heating contained 0.09 mM Mn (attributed to experimental error in solution preparation). This difference in concentration is sufficient to explain most of the relaxation difference between the datasets. While small differences in Mn concentrations were also seen in the samples nominally containing 1.0 mM of Mn²⁺, the sample containing 0.99 mM Mn added pre-heating produced slower relaxation rates than both samples containing 0.98 mM Mn added post-heating. This suggests that paramagnetic samples underwent more degradation than diamagnetic samples; i.e., the Mn(TFSI)2 addition caused an albeit small amount of additional electrolyte degradation.

The samples were then diluted 10× with d₆-DMSO to improve the visibility of the degradation peaks, as has been discussed elsewhere. 117 Further NMR analysis concerning the effects of deuterated solvents, including d₆-DMSO, CD₃CN, and MeOD, on the Mn²⁺ solvation shell is provided in the SI (Fig. S7); the most significant effects are observed with DMSO, which appears to displace EC from the solvation shell. The resulting ¹⁹F spectra were used to estimate the concentrations of PO₂F₂⁻ and HF (Fig. 7b). These are still only estimates, as the d₆-DMSO does not completely prevent the broadening of degradation peaks; hence, comparisons are only drawn between samples containing the same Mn2+ concentrations, and not between the 0.1 and 1.0 mM datasets. In all cases, the PO₂F₂ and HF concentrations are larger in the samples that were heated in the presence of Mn²⁺. It is possible that some of the degradation enhancement is due to the Mn(TFSI)2 addition requiring several transfers during the preparation and dilution of stock solutions, which may have caused minor contamination from trace adsorbed water on vial or pipette surfaces, despite work being carried out in an argon glovebox. That said, the degradation enhancement is larger when more Mn²⁺ is present: there is a $\sim 10\%$ increase in $PO_2F_2^-$ concentration and \sim 19% increase in HF concentration with 0.1 mM Mn²⁺ added, and a $\sim 30\%$ increase in PO₂F₂⁻ concentration and $\sim 59\%$ increase in HF concentration with 1.0 mM Mn²⁺ added, even with potential underestimation of degradation species at 1.0 mM due to signal broadening. The apparent dose-response relationship confirms that at least some of the degradation enhancement is specifically due to the Mn(TFSI)2, consistent with the relaxometry results in Fig. 7a.

Previous work on electrolytes heated with 0 versus 100 or 300 mM Mn²⁺ has shown a dramatic effect of Mn²⁺ on electrolyte degradation, with paramagnetic solutions turning brown after 8 days at 55 °C. 8,14 It was proposed that Mn²⁺ coordination to PF₆⁻ facilitated the formation of reactive PF₅.8 (We note that a brown discolouration may also indicate MnO2 formation and possibly oxygen/water contamination.) In comparison, the degradation of samples in our work is relatively minor, particularly considering that samples were heated at 60 °C for ten weeks. No difference in colouration was observed between diamagnetic and paramagnetic samples after heating. The EPR and NMR data (Fig. 2 and 5, respectively) clearly show that Mn²⁺ preferentially interacts with PO₂F₂⁻ over PF₆⁻ in the inner coordination shell, which is also confirmed by DFT calculations (Table S2). At small Mn2+ concentrations, such as those used in this work, the probability that PF₆ enters the Mn²⁺ inner coordination shell once Mn²⁺ is surrounded by PO₂F₂ may be reduced significantly, consistent with the ¹⁹F NMR studies. Thus, the PF₆ decomposition effect may become self-limiting, especially in cases where LiPO₂F₂ is used as an electrolyte additive. At the large Mn²⁺ concentrations used in previous studies, far more PO2F2 would be required to coordinate all Mn^{2^+} , and complete coordination to $\mathrm{PO_2F_2}^-$ may not be possible, resulting in "free" Mn2+ and far more electrolyte degradation. The dissolved Mn²⁺ concentration in cells is generally small as Mn2+ migrates to the negative electrode and

deposits there; furthermore, when dissolution occurs in situ into an already-degraded electrolyte, PO2F2- may already exist in solution, which is not the case when Mn2+ model compounds are added to pristine electrolyte. Therefore, while the results in Fig. 7 are consistent with previous observations of Mn²⁺-induced electrolyte degradation, it also appears that this effect is unlikely to be a main contributor to electrolyte degradation in cells, with most of the harm of dissolved transition metals occurring once they are deposited at the anode. These results also show that NMR relaxometry may be used in these systems as a probe for electrolyte degradation, as long as the concentration of paramagnetic ions is constant; this method may also be applied in other systems, if a degradation product coordinates more closely to the transition metal ions than to the pristine electrolyte species.

ICP-OES experiments of transition metal metathesis. Our studies of transition metal coordination to a wider range of anionic species in solution were complicated by the low solubility of many lithium salts, as well as the finding that the addition of many lithium salts induces precipitation of transition metals. Thus, the effect of a large series of lithium salts-some of which have been shown to be present in the SEI—on transition metal solubility was investigated.

Fig. 8 shows ICP-OES results for the concentration of Mn²⁺ or Ni²⁺ in 3:7 EC: EMC (v/v) after 1 mM solutions were shaken with various lithium salts and stored for two days. All lithium salts studied induced some amount of transition metal precipitation, including the organic lithium salts, suggesting that metals may be able to precipitate directly in both the outer organic SEI and the inner inorganic SEI. The addition of Li₂O₂ to Mn²⁺-containing solution resulted in the solution

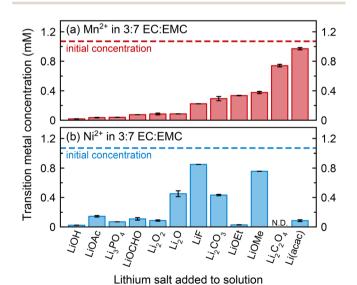


Fig. 8 (a) Mn²⁺ or (b) Ni²⁺ concentrations in 3:7 EC:EMC (v/v) solutions after lithium salts were added to solutions containing ~1 mM of Mn(TFSI)₂ or Ni(TFSI)2. The initial concentration is indicated by the dashed line (1.07 mM for both Mn²⁺ and Ni²⁺); bars indicate the new transition metal concentration two days after lithium salt addition. All concentrations were measured by ICP-OES. Error bars show the range obtained for duplicate experiments (i.e., measurements on two different solutions)

immediately turning brown in colour, likely due to the oxidation of Mn2+ to yield the brown MnO2 precipitate. The largest differences between Ni2+ and Mn2+ precipitation behaviour were observed with Li₂O, LiF, and LiOMe, where more Mn²⁺ precipitation occurred, and with LiOEt and Li(acac), where more Ni²⁺ precipitation occurred. Generally, this seems to suggest a possible preference for Mn2+ precipitation with harder, more inorganic components, and Ni²⁺ precipitation with softer, more organic components, which is consistent with the classification of Mn2+ as a hard cation and Ni2+ as borderline. 118,119 This may explain why some studies that have examined metals both in the electrolyte solution and on the anode surface have shown that a greater fraction of dissolved Mn2+ is deposited compared to dissolved Ni2+ or Co2+41,120 Interestingly, with Li(acac), not only did \sim 91% of Mn²⁺ remain in solution, but the lithium concentration in solution increased from 0.474 ± 0.004 mM when Li(acac) was stored in a diamagnetic solution to 3.43 \pm 0.02 mM when Li(acac) was stored in a Mn²⁺-containing solution; i.e., an additional 2.96 mM Li dissolved, or ~3:1 Li:Mn ratio. This enhanced Li dissolution suggests that Li/Mn exchange occurs, and Mn2+ chelation by acac is favourable, but the product is soluble. This ICP-OES result also supports the interpretation of the relaxometry results in Fig. 6b.

While previous studies have exposed transition metal ions to cycled graphite anodes, 73,75-79 specific learnings from those experiments are complicated by the fact that the exact SEI composition is unknown, and it is therefore unknown which species the transition metal ions are exchanging with. We also note that the exact nature of an SEI greatly depends on the specific electrolyte composition used and particularly any SEI additives employed. This experiment expands on that previous work, as well as previous work studying ex situ exchange with some inorganic lithium salts, 39,74,75 revealing that transition metals can exchange with many different species, including organic salts.

The ICP-OES results show that various SEI salts can induce transition metal precipitation out of EC: EMC solution, lending credence to metathesis deposition mechanisms. (We note that this is not necessarily mutually exclusive with possible reduction mechanisms; the first step for any reduction that may occur is initial incorporation into the SEI, and one such mechanism occurs via ion exchange.) However, when metals are surrounded by suitably coordinating species in a degraded electrolyte solution, such as PO2F2-/HPO2F2, desolvation and precipitation at the anode surface may become less favourable. More exchange-type experiments that are explicitly conducted in the presence of degradation species such as PO₂F₂⁻ may help determine the realistic likelihood of transition metal metathesis. The combined EPR, NMR, and ICP-OES results in this work present a spectrum of coordination behaviour that influences transition metal deposition. With species like PF₆⁻, Mn²⁺ coordination is not preferred; with species like PO2F2- or acac-, Mn2+ coordination is preferred but the complexes are soluble; and with species like PO₄³⁻ or OH⁻, Mn²⁺ precipitates almost completely. The location where dissolved transition

metals ultimately precipitate will likely depend on which species are nearby: if a favourable species encouraging precipitation is present when Mn²⁺ dissolves, it will more likely deposit on the cathode or separator; otherwise, Mn²⁺ may bind to species in solution and either remain in solution or deposit on the anode, depending on the strength and favourability of coordination. A clearer understanding of transition metal complexation behaviours in battery electrolytes may facilitate strategies that prevent transition metal dissolution, encourage precipitation of metal ions at the cathode, and/or enable sequestration of metal ions in solution, ultimately preventing deposition and harmful reactions at the anode.

Conclusions

Paramagnetic solution NMR and pulsed one and twodimensional EPR and ENDOR were used to probe the coordination of Mn²⁺ and Ni²⁺ in degraded electrolytes, probing the electron-nuclear interactions from two perspectives. Heatdegraded electrolyte solutions, or solutions containing simulated degradation species, were examined to unravel transition metal coordination to specific solution components of interest. Although in pristine electrolyte solutions the solvation shell is mainly comprised of the solvent molecule EC, the transition metal solvation shell is considerably changed in degraded electrolyte solutions; these results illustrate the power of this joint approach in determining the structures of metal complexes in pristine and degraded electrolytes.

Pulsed EPR experiments of frozen solutions show that in heat- and water-degraded LiPF₆ electrolytes, Mn²⁺ is coordinated to a combination of anionic and protonated fluorophosphate species. This is consistent with measurements of NMR relaxation rates showing that EC and PF₆ are increasingly displaced in the Mn²⁺ and Ni²⁺ inner and outer coordination spheres when electrolytes are heated. When water or D2O is added to pristine, non-degraded electrolyte solutions containing either LiPF6 or LiTFSI salts, EPR experiments show that it enters the Mn²⁺ first coordination sphere and displaces EC to form $[Mn(OH_2)_6]^{2^+}/[Mn(OD_2)_6]^{2^+}$; however, in LiPF₆-containing electrolytes, the protonated fluorophosphate species that arise from PF₆ hydrolysis, specifically HPO₂F₂, ultimately displace the water from the first coordination shell. The electron-¹H hyperfine coupling tensors obtained by simulations of the ENDOR experiments indicate a Mn-H distance of between 3.7 and 4.8 Å, consistent with an HPO₂F₂ inner sphere complex. EPR and NMR of solutions containing added LiPO₂F₂ complement the results from heated electrolyte solutions, indicating that PO₂F₂⁻ is present in both inner sphere and outer sphere Mn²⁺ complexes.

While EPR experiments of frozen solutions allow for a more detailed structural analysis of Mn²⁺ complex formation, the use of NMR relaxometry permits a more rapid screening of the effect of additives and electrolyte degradation on complex formation. For example, NMR experiments showed that the addition of ethylene glycol to the electrolyte causes the

displacement of EC in the first solvation shell of Mn²⁺ and Ni²⁺ (as seen for PO₂F₂⁻), now also reducing the size of the first solvation shell. Addition of the larger acetylacetonate ligand displaced both EC and PF₆-. Examination of samples heated with and without Mn²⁺ indicated that dissolved transition metals likely do not contribute significantly to decomposition of the bulk electrolyte solution in the period after dissolution and before deposition, as has been previously suggested. This is because transition metals are present in small concentrations and coordination to typical electrolyte degradation species is preferred over coordination to, and decomposition of, pristine electrolyte components. Lastly, ICP-OES experiments targeting the strength and extent of transition metal coordination showed that many lithium-containing salts proposed to be present in the SEI appear to induce some amount of transition metal exchange, typically associated with precipitation of the corresponding transition metal salts.

This work demonstrates the importance of considering degradation species in the transition metal solvation shell, which must be considered when designing representative experimental model systems and when performing computational work. This work also supports the metathesis mechanism of transition metal incorporation into the SEI, while identifying differences in how Mn²⁺ and Ni²⁺ are desolvated, which may affect the likelihood of metal deposition and the activity of deposited metals towards electrolyte decomposition. The phenomenon of transition metal coordination to solution degradation species that is shown in this work may present an additional, largely overlooked mechanism for dissolution behaviour. New insights about transition metal coordination may be leveraged to reduce transition metal dissolution and deposition, preventing battery degradation and extending lifetime.

Conflicts of interest

There are no conflicts to declare.

Data availability

In addition to the NMR, EPR, and DFT figures and tables in the supplementary information (SI), we include ZIP files with further supporting data for EPR and DFT studies of Mn coordination. These include CSV files with hyperfine coupling constants and XYZ files with final structures of all complexes. Supplementary information: Further DFT calculations, experimental and simulated EPR spectra, and NMR relaxometry. See DOI: https://doi.org/10.1039/d5ee01250c.

Acknowledgements

JPA thanks the Natural Sciences and Engineering Research Council of Canada for funding; JPA and CPG acknowledge support from the Faraday Institution under grant number FIRG001 and from the Royal Society *via* a professorship to CPG; CS acknowledges computing resources granted by RWTH

Aachen University under project rwth0701; EJ and CPG acknowledge support from the ERC grant BATNMR no 835073.

Notes and references

- 1 W. Choi and A. Manthiram, *J. Electrochem. Soc.*, 2006, **153**, A1760.
- 2 H. Zheng, Q. Sun, G. Liu, X. Song and V. S. Battaglia, J. Power Sources, 2012, 207, 134–140.
- 3 J. A. Gilbert, I. A. Shkrob and D. P. Abraham, J. Electrochem. Soc., 2017, 164, A389–A399.
- 4 C. Zhan, T. Wu, J. Lu and K. Amine, *Energy Environ. Sci.*, 2018, **11**, 243–257.
- 5 R. Jung, F. Linsenmann, R. Thomas, J. Wandt, S. Solchenbach, F. Maglia, C. Stinner, M. Tromp and H. A. Gasteiger, J. Electrochem. Soc., 2019, 166, A378–A389.
- 6 O. C. Harris, S. E. Lee, C. Lees and M. Tang, *JPhys Energy*, 2020, 2, 032002.
- 7 Y.-K. Han, K. Lee, S. Kang, Y. S. Huh and H. Lee, *Comput. Mater. Sci.*, 2014, 81, 548–550.
- 8 C. Wang, L. Xing, J. Vatamanu, Z. Chen, G. Lan, W. Li and K. Xu, *Nat. Commun.*, 2019, **10**, 3423.
- X. Cui, J. Sun, D. Zhao, J. Zhang, J. Wang, H. Dong,
 P. Wang, J. Zhang, S. Wu, L. Song, N. Zhang, C. Li and
 S. Li, *J. Energy Chem.*, 2023, 78, 381–392.
- 10 S.-B. Son, Z. Zhang, J. Gim, C. S. Johnson, Y. Tsai, M. Kalensky, S. Lopykinski, O. Kahvecioglu, Z. Yang, A. T. Montoya and I. Bloom, J. Phys. Chem. C, 2023, 127, 1767–1775.
- 11 J. P. Allen, C. Szczuka, H. E. Smith, E. Jónsson, R.-A. Eichel, J. Granwehr and C. P. Grey, *Phys. Chem. Chem. Phys.*, 2024, 26, 19505–19520.
- 12 A. Jarry, S. Gottis, Y.-S. Yu, J. Roque-Rosell, C. Kim, J. Cabana, J. Kerr and R. Kostecki, *J. Am. Chem. Soc.*, 2015, 137, 3533–3539.
- 13 I. A. Shkrob, A. J. Kropf, T. W. Marin, Y. Li, O. G. Poluektov, J. Niklas and D. P. Abraham, *J. Phys. Chem. C*, 2014, **118**, 24335–24348.
- 14 X. Luo, L. Xing, J. Vatamanu, J. Chen, J. Chen, M. Liu, C. Wang, K. Xu and W. Li, *J. Energy Chem.*, 2022, 65, 1–8.
- A. Du Pasquier, A. Blyr, P. Courjal, D. Larcher, G. Amatucci,
 B. Gérand and J.-M. Tarascon, *J. Electrochem. Soc.*, 1999,
 146, 428–436.
- 16 D. R. Gallus, R. Schmitz, R. Wagner, B. Hoffmann, S. Nowak, I. Cekic-Laskovic, R. W. Schmitz and M. Winter, *Electrochim. Acta*, 2014, 134, 393–398.
- 17 D. Huang, C. Engtrakul, S. Nanayakkara, D. W. Mulder, S.-D. Han, M. Zhou, H. Luo and R. C. Tenent, ACS Appl. Mater. Interfaces, 2021, 13, 11930–11939.
- 18 J. C. Hestenes, J. T. Sadowski, R. May and L. E. Marbella, ACS Mater. Au, 2023, 3, 88–101.
- 19 Y. Tesfamhret, H. Liu, E. J. Berg and R. Younesi, *RSC Adv.*, 2023, **13**, 20520–20529.
- 20 L. J. Reinschlüssel, L. Reuter, P. Rapp, M. Bock, A. Berger, M. A. Schilling and H. A. Gasteiger, *J. Electrochem. Soc.*, 2025, 172, 060536.

Paper

- 21 K. Leung, Chem. Mater., 2017, 29, 2550-2562.
- 22 N. N. Intan, K. Klyukin and V. Alexandrov, ACS Appl. Mater. Interfaces, 2019, 11, 20110–20116.
- 23 H. R. Morin, D. G. Graczyk, Y. Tsai, S. Lopykinski, H. Iddir, J. C. Garcia, N. Dietz Rago, S. Trask, L. Flores, S.-B. Son, Z. Zhang, N. M. Johnson and I. Bloom, ACS Appl. Energy Mater., 2020, 3, 2565–2575.
- 24 R. Sahore, D. C. O'Hanlon, A. Tornheim, C.-W. Lee, J. C. Garcia, H. Iddir, M. Balasubramanian and I. Bloom, J. Electrochem. Soc., 2020, 167, 020513.
- J. Lüchtefeld, H. Hemmelmann, S. Wachs, K. J. Mayrhofer,
 M. T. Elm and B. B. Berkes, J. Phys. Chem. C, 2022, 126, 17204–17211.
- 26 J. Lüchtefeld, M.-Y. Lee, H. Hemmelmann, S. Wachs, C. Behling, K. J. J. Mayrhofer, M. T. Elm and B. B. Berkes, ACS Omega, 2023, 8, 32606–32614.
- 27 C. L. Campion, W. Li, W. B. Euler, B. L. Lucht, B. Ravdel, J. F. DiCarlo, R. Gitzendanner and K. M. Abraham, *Electro-chem. Solid-State Lett.*, 2004, 7, A194.
- 28 C. L. Campion, W. Li and B. L. Lucht, *J. Electrochem. Soc.*, 2005, **152**, A2327–A2334.
- 29 A. V. Plakhotnyk, L. Ernst and R. Schmutzler, *J. Fluorine Chem.*, 2005, **126**, 27–31.
- 30 S. Wiemers-Meyer, M. Winter and S. Nowak, *Phys. Chem. Chem. Phys.*, 2016, **18**, 26595–26601.
- 31 K. Nagayama, K. Kamioka, E. Iwata, H. Oka, Y. Tokunaga and T. Okada, *Electrochemistry*, 2001, **69**, 6–9.
- 32 S. Klein, P. Harte, S. van Wickeren, K. Borzutzki, S. Röser, P. Bärmann, S. Nowak, M. Winter, T. Placke and J. Kasnatscheew, *Cell Rep. Phys. Sci.*, 2021, 2, 100521.
- 33 J. Chen, L. Xing, X. Yang, X. Liu, T. Li and W. Li, *Electro-chim. Acta*, 2018, **290**, 568–576.
- 34 C. Wang, L. Yu, W. Fan, J. Liu, L. Ouyang, L. Yang and M. Zhu, ACS Appl. Energy Mater., 2018, 1, 2647–2656.
- 35 S. Klein, L. Haneke, P. Harte, L. Stolz, S. van Wickeren, K. Borzutzki, S. Nowak, M. Winter, T. Placke and J. Kasnatscheew, *ChemElectroChem*, 2022, 9, e202200469.
- 36 B. Yang, H. Zhang, L. Yu, W. Fan and D. Huang, *Electro-chim. Acta*, 2016, **221**, 107–114.
- 37 G. Yang, J. Shi, C. Shen, S. Wang, L. Xia, H. Hu, H. Luo, Y. Xia and Z. Liu, *RSC Adv.*, 2017, 7, 26052–26059.
- 38 W. Zhao, G. Zheng, M. Lin, W. Zhao, D. Li, X. Guan, Y. Ji, G. F. Ortiz and Y. Yang, *J. Power Sources*, 2018, 380, 149–157.
- 39 S. Klein, P. Harte, J. Henschel, P. Bärmann, K. Borzutzki, T. Beuse, S. van Wickeren, B. Heidrich, J. Kasnatscheew, S. Nowak, M. Winter and T. Placke, *Adv. Energy Mater.*, 2021, 11, 2003756.
- 40 S. Klein, S. van Wickeren, S. Röser, P. Bärmann, K. Borzutzki, B. Heidrich, M. Börner, M. Winter, T. Placke and J. Kasnatscheew, Adv. Energy Mater., 2021, 11, 2003738.
- 41 Y. Tesfamhret, PhD thesis, Uppsala University, 2022.
- 42 H. Kim, J. G. Lee, S.-M. Kim, J. Kim, J. Soon, J. B. Lee, J. Mun, J. H. Ryu and S. M. Oh, *Meet. Abstr.*, 2016, MA2016-03, 1049.

- 43 S. Y. Park, S. Park, H. Y. Lim, M. Yoon, J. Choi, S. K. Kwak, S. Y. Hong and N. Choi, Adv. Sci., 2023, 10, 2205918.
- 44 Y.-G. Cho, S. H. Jung, J. Jeong, H. Cha, K. Baek, J. Sung, M. Kim, H. T. Lee, H. Kong, J. Cho, S. J. Kang, J. M. Park and H.-K. Song, *ACS Appl. Mater. Interfaces*, 2021, 13, 9965–9974.
- 45 A. Banerjee, Y. Shilina, B. Ziv, J. M. Ziegelbauer, S. Luski, D. Aurbach and I. C. Halalay, J. Electrochem. Soc., 2017, 164, A6315–A6323.
- 46 J. Seo, J. Im, M. Kim, D. Song, S. Yoon and K. Y. Cho, *Small*, 2024, **20**, 2312132.
- 47 M.-H. Ryou, S. Hong, M. Winter, H. Lee and J. W. Choi, J. Mater. Chem. A, 2013, 1, 15224.
- 48 T. Dong, P. Mu, S. Zhang, H. Zhang, W. Liu and G. Cui, Electrochem. Energ. Rev., 2021, 4, 545-565.
- 49 N.-Y. Kim, J. Moon, M.-H. Ryou, S.-H. Kim, J.-H. Kim, J.-M. Kim, J. Bang and S.-Y. Lee, *Adv. Energy Mater.*, 2022, 12, 2102109.
- 50 C. Zou, Y. Huang, L. Zhao, W. Ren, Z. Zhao, J. Liu, X. Li, M. Wang, B. Guo and Y. Lin, ACS Appl. Mater. Interfaces, 2022, 14, 14226–14234.
- 51 H. Saneifar, K. Zaghib and D. Bélanger, ACS Appl. Energy Mater., 2020, 3, 647–657.
- 52 G. G. Amatucci, A. Blyr, C. Sigala, P. Alfonse and J. M. Tarascon, *Solid State Ionics*, 1997, **104**, 13–25.
- 53 A. Blyr, A. Du Pasquier, G. Amatucci and J.-M. Tarascon, *Ionics*, 1997, 3, 321–331.
- 54 S. Solchenbach, G. Hong, A. T. S. Freiberg, R. Jung and H. A. Gasteiger, *J. Electrochem. Soc.*, 2018, **165**, A3304–A3312.
- 55 O. C. Harris, Y. Lin, Y. Qi, K. Leung and M. H. Tang, J. Electrochem. Soc., 2020, 167, 013502.
- 56 X. Zhang, Z. Cui and A. Manthiram, *Adv. Energy Mater.*, 2022, 2103611.
- 57 Y. Terada, Y. Nishiwaki, I. Nakai and F. Nishikawa, *J. Power Sources*, 2001, 97–98, 420–422.
- 58 J. Wandt, A. Freiberg, R. Thomas, Y. Gorlin, A. Siebel, R. Jung, H. A. Gasteiger and M. Tromp, *J. Mater. Chem. A*, 2016, 4, 18300–18305.
- 59 L. Hanf, J. Henschel, M. Diehl, M. Winter and S. Nowak, *Electrophoresis*, 2020, **41**, 697–704.
- 60 J. P. Allen and C. P. Grey, Chem. Commun., 2023, 59, 1677–1680.
- 61 A. Abragam and B. Bleaney, *Electron Paramagnetic Resonance of Transition Ions*, Clarendon Press, 1970.
- 62 I. Bertini, C. Luchinat, G. Parigi and E. Ravera, NMR of Paramagnetic Molecules: Applications to Metallobiomolecules and Models, Elsevier, 2016.
- 63 M. Jiang, B. Key, Y. S. Meng and C. P. Grey, *Chem. Mater.*, 2009, 21, 2733–2745.
- 64 R. Jung, M. Metzger, F. Maglia, C. Stinner and H. A. Gasteiger, J. Electrochem. Soc., 2017, 164, A1361–A1377.
- 65 A. T. S. Freiberg, M. K. Roos, J. Wandt, R. de Vivie-Riedle and H. A. Gasteiger, J. Phys. Chem. A, 2018, 122, 8828–8839.
- 66 X. Ren, J. Wang, Z. Peng and L. Lu, Chem. Sci., 2018, 9, 231-237.
- 67 Y. Yu, P. Karayaylali, Y. Katayama, L. Giordano, M. Gauthier, F. Maglia, R. Jung, I. Lund and Y. Shao-Horn, *J. Phys. Chem. C*, 2018, **122**, 27368–27382.

- 68 U. Heider, R. Oesten and M. Jungnitz, *J. Power Sources*, 1999, **81-82**, 119-122.
- 69 M. Metzger, B. Strehle, S. Solchenbach and H. A. Gasteiger, J. Electrochem. Soc., 2016, 163, A1219.
- 70 C. Szczuka, R.-A. Eichel and J. Granwehr, ACS Appl. Energy Mater., 2022, 5, 449–460.
- 71 L. Liu, S. Gu, S. Wang, X. Zhang and S. Chen, *RSC Adv.*, 2020, **10**, 1704–1710.
- 72 Z. Ruff, C. Xu and C. P. Grey, *J. Electrochem. Soc.*, 2021, **168**, 060518.
- 73 C. Zhan, J. Lu, A. J. Kropf, T. Wu, A. N. Jansen, Y.-K. Sun, X. Qiu and K. Amine, *Nat. Commun.*, 2013, 4, 2437.
- 74 H. Shin, J. Park, A. M. Sastry and W. Lu, J. Power Sources, 2015, 284, 416-427.
- 75 D. R. Vissers, Z. Chen, Y. Shao, M. Engelhard, U. Das, P. Redfern, L. A. Curtiss, B. Pan, J. Liu and K. Amine, ACS Appl. Mater. Interfaces, 2016, 8, 14244-14251.
- 76 C. Zhan, X. Qiu, J. Lu and K. Amine, Adv. Mater. Interfaces, 2016, 3, 1500856.
- 77 V. Meunier, M. L. D. Souza, M. Morcrette and A. Grimaud, *J. Electrochem. Soc.*, 2022, **169**, 070506.
- 78 H. Xu, Z. Li, T. Liu, C. Han, C. Guo, H. Zhao, Q. Li, J. Lu, K. Amine and X. Qiu, *Angew. Chem., Int. Ed.*, 2022, 61, e202202894.
- 79 Q. Xie, J. Chen, L. Xing, X. Zhou, Z. Ma, B. Wu, Y. Lin, H. Zhou and W. Li, J. Energy Chem., 2022, 69, 389–396.
- 80 P. Lu and S. J. Harris, *Electrochem. Commun.*, 2011, 13, 1035–1037.
- 81 P. Höfer, A. Grupp, H. Nebenführ and M. Mehring, *Chem. Phys. Lett.*, 1986, **132**, 279–282.
- 82 F. Neese, Wiley Interdiscip. Rev.: Comput. Mol. Sci., 2022, 12, e1606.
- 83 J. Tao, J. P. Perdew, V. N. Staroverov and G. E. Scuseria, *Phys. Rev. Lett.*, 2003, **91**, 146401.
- 84 V. N. Staroverov, G. E. Scuseria, J. Tao and J. P. Perdew, J. Chem. Phys., 2003, 119, 12129–12137.
- 85 E. Van Lenthe, E. J. Baerends and J. G. Snijders, *J. Chem. Phys.*, 1993, **99**, 4597–4610.
- 86 R. Van Leeuwen, E. Van Lenthe, E. J. Baerends and J. G. Snijders, J. Chem. Phys., 1994, 101, 1272–1281.
- 87 F. Weigend and R. Ahlrichs, *Phys. Chem. Chem. Phys.*, 2005, 7, 3297–3305.
- 88 D. A. Pantazis, X.-Y. Chen, C. R. Landis and F. Neese, *J. Chem. Theory Comput.*, 2008, 4, 908–919.
- 89 C. Adamo and V. Barone, J. Chem. Phys., 1999, 110, 6158-6170.
- 90 F. Neese, Inorg. Chim. Acta, 2002, 337, 181-192.
- 91 N.-A. Stamos, E. Ferentinos, M. Chrysina, C. P. Raptopoulou, V. Psycharis, Y. Sanakis, D. A. Pantazis, P. Kyritsis and G. Mitrikas, *Inorg. Chem.*, 2020, **59**, 3666–3676.
- 92 F. Neese, J. Chem. Phys., 2005, 122, 034107.
- 93 S. Stoll and A. Schweiger, J. Magn. Reson., 2006, 178, 42-55.
- 94 S. Stoll and R. D. Britt, *Phys. Chem. Chem. Phys.*, 2009, **11**, 6614–6625.

- 95 C. Fan, P. E. Doan, C. E. Davoust and B. M. Hoffman, J. Magn. Reson. (1969), 1992, 98, 62-72.
- 96 P. E. Doan, N. S. Lees, M. Shanmugam and B. M. Hoffman, Appl. Magn. Reson., 2010, 37, 763–779.
- 97 H. Y. Carr and E. M. Purcell, Phys. Rev., 1954, 94, 630-638.
- 98 S. Meiboom and D. Gill, Rev. Sci. Instrum., 1958, 29, 688-691.
- 99 T. A. Stich, S. Lahiri, G. Yeagle, M. Dicus, M. Brynda, A. Gunn, C. Aznar, V. J. DeRose and R. D. Britt, *Appl. Magn. Reson.*, 2007, 31, 321–341.
- T. M. Atkins, J. H. Walton, M. P. Singh, S. Ganguly,
 O. Janka, A. Y. Louie and S. M. Kauzlarich, *J. Phys. Chem. C*, 2017, 121, 1948–1956.
- 101 C. Duboc, M.-N. Collomb and F. Neese, Appl. Magn. Reson., 2010, 37, 229–245.
- 102 J. W. Larson and B. Su, J. Chem. Eng. Data, 1994, 39, 33-35.
- 103 C. Szczuka, P. Jakes, R.-A. Eichel and J. Granwehr, *Adv. Energy Sustainability Res.*, 2021, 2, 2100121.
- 104 S. A. Dikanov and A. T. Taguchi, Appl. Magn. Reson., 2020, 51, 1177–1200.
- 105 A. Pöppl and L. Kevan, J. Phys. Chem., 1996, 100, 3387-3394.
- 106 F. Neese, J. Chem. Phys., 2003, 118, 3939-3948.
- 107 M. L. Munzarova, P. Kubacek and M. Kaupp, J. Am. Chem. Soc., 2000, 122, 11900–11913.
- 108 M. Kubot, L. Frankenstein, E. Muschiol, S. Klein, M. Esselen, M. Winter, S. Nowak and J. Kasnatscheew, *Chem-SusChem*, 2022, e202202189.
- 109 G. Gachot, P. Ribière, D. Mathiron, S. Grugeon, M. Armand, J.-B. Leriche, S. Pilard and S. Laruelle, *Anal. Chem.*, 2011, 83, 478–485.
- 110 V. Kraft, W. Weber, M. Grützke, M. Winter and S. Nowak, *RSC Adv.*, 2015, 5, 80150–80157.
- 111 S. Van Doorslaer, *eMagRes*, John Wiley & Sons, Ltd, Chichester, UK, 2017, vol. 6, pp. 51–70.
- 112 D. van Ormondt, R. de Beer, M. Brouha and F. de Groot, Z. Naturforsch., A, 1969, 24, 1746–1751.
- 113 S. Un, Inorg. Chem., 2013, 52, 3803-3813.
- 114 A. J. Pell, G. Pintacuda and C. P. Grey, *Prog. Nucl. Magn. Reson. Spectrosc.*, 2019, 111, 1–271.
- 115 J. P. Allen, C. A. O'Keefe and C. P. Grey, *J. Phys. Chem. C*, 2023, **127**, 9509–9521.
- 116 J. Zhang, X. Yao, R. K. Misra, Q. Cai and Y. Zhao, *J. Mater. Sci. Technol.*, 2020, 44, 237–257.
- 117 J. P. Allen and C. P. Grey, *J. Phys. Chem. C*, 2023, **127**, 4425–4438.
- 118 S. F. A. Kettle, *Coordination Compounds*, Thomas Nelson and Sons, London, 1969.
- 119 J. E. Huheey, E. A. Keiter and R. L. Keiter, *Inorganic Chemistry: Principles of Structure and Reactivity*, HarperCollins College Publishers, New York, 4th edn, 1993.
- 120 W. M. Dose, I. Temprano, J. P. Allen, E. Björklund, C. A. O'Keefe, W. Li, B. L. Mehdi, R. S. Weatherup, M. F. L. De Volder and C. P. Grey, *ACS Appl. Mater. Interfaces*, 2022, 14, 13206–13222.