

Cite this: *RSC Adv.*, 2018, **8**, 13018

## Positively charged and flexible $\text{SiO}_2@\text{ZrO}_2$ nanofibrous membranes and their application in adsorption and separation†

Yafei Tang, Zhaowei Liu, Kang Zhao \* and Song Fu

Tiny particles with a negative charge in water can be removed effectively by inorganic positively charged nanofiber membranes due to their physical separation and electrostatic adsorption properties. However, the charged positive and isoelectric points (IEP) on the surface of the positively charged nanofiber membranes need to be further improved to meet the requirements of the Environmental Protection Agency for virus filters (excellent adsorption and separation properties in solutions with pH between 5 and 9). The positively charged  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membrane was fabricated by electrospinning combined with the impregnation method and calcined in an anoxic atmosphere. The effects of the impregnating solution concentration and centrifugal speeds on the morphology, pore size and nanofiber diameter of the composite nanofibrous membrane were investigated. The phase composition, the element valence state, the surface charge and the adsorption separation properties of the composite nanofibrous membranes were characterized. Flexible  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes with high specific surface area and water flux were obtained. The surface isoelectric point is 7.3 when calcined in a mixed atmosphere of  $\text{N}_2$  (96%)/ $\text{H}_2$  (4%), which is higher than that when calcined in air and vacuum. Some oxygen vacancies were present on the surface of the  $\text{ZrO}_x$  ( $0 < x < 2$ ) shell, resulting in the tetragonal zirconia still being available at room temperature. The interception rate of the positively charged  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes for a titan yellow solution with a concentration of  $10 \text{ mg L}^{-1}$  reaches 99.996%. Its maximum adsorption capacity can reach  $63.27 \text{ mg cm}^{-3}$  when filtering a 1 L titan yellow solution. The resulting nanofibrous membranes have potential application for the separation of bacteria and viruses from water.

Received 4th March 2018  
Accepted 2nd April 2018

DOI: 10.1039/c8ra01899e  
[rsc.li/rsc-advances](http://rsc.li/rsc-advances)

### Introduction

Adsorption and separation materials are widely used in sewage purification, mineral water removal of bacteria and gas purification.<sup>1,2</sup> Porous ceramic materials have attracted much attention in the field of filtration and separation because of their excellent properties such as chemical stability, high temperature resistance, and corrosion resistance.<sup>3,4</sup> Generally, the objects removed to achieve the goal of purification by porous ceramic materials were removed based on the ceramic porous structure, mainly through physical adsorption and interception.<sup>5,6</sup> Therefore, the open porosity and specific surface area of porous ceramic materials are important factors that can affect the filtration efficiency.<sup>7,8</sup> Many methods have been used to prepare porous ceramic materials with high open porosity and high specific surface area, such as dip-molding and freeze

casting.<sup>9–11</sup> The porous ceramics obtained by these methods can remove impurities of a large size only. However, for some small size particles, such as dyes (<100 nm), bacteria (<1  $\mu\text{m}$ ) and viruses (<100 nm), adsorption and interception properties have been found to be poor mainly because of the large size of the pores (>2  $\mu\text{m}$ ) of porous ceramics.<sup>12–14</sup>

Electrospinning is a method of preparing nanofibers using a high voltage electrostatic field.<sup>15,16</sup> The spinnable polymer and the ceramic precursor were mixed to prepare a spinning solution, and then porous ceramic fibrous membranes were obtained after calcination.<sup>17,18</sup> The pore size of the porous fibrous membranes was usually not greater than 1  $\mu\text{m}$ , the electrospun material does not form closed pores, and a high specific surface area can be obtained.<sup>19,20</sup> Porous fibrous membranes can be used as the separation material through their physical sieving effect of the pores. Smaller pore size corresponds to better filtration and separation performance. However, the water flux is low when the pore size is too low, and the liquid requires high pressure to pass through the membrane. The stability of the ceramic fibrous membrane will also be reduced due to its brittleness. If the surface of the porous fibrous membranes is positively charged, negative particles would be adsorbed and

Department of Materials Science and Engineering, Xi'an University of Technology, Xi'an 710048, PR China. E-mail: [kzhao@xaut.edu.cn](mailto:kzhao@xaut.edu.cn); Fax: +86-29-82312922; Tel: +86-29-82312922

† Electronic supplementary information (ESI) available. See DOI: [10.1039/c8ra01899e](https://doi.org/10.1039/c8ra01899e)



removed by electrostatic adsorption.<sup>21,22</sup> It is possible to adsorb small size bacteria ( $<1\text{ }\mu\text{m}$ ) and viruses ( $<100\text{ nm}$ ) with negative charged surface using large pore size (100 nm to 2  $\mu\text{m}$ ) materials with positive charged (above the isoelectric point in solutions). In previous work, we have used the electrostatic spinning to fabricate the  $\text{ZrO}_2$  nanofibrous microfiltration membrane.<sup>23</sup> The isoelectric point is only 4.3, and the separation range of the  $\text{ZrO}_2$  nanofibrous microfiltration membrane was narrow. The isoelectric point of the  $\text{ZrO}_2$  nanofiber can be increased by calcining in the vacuum but only up to 4.7. In the vacuum calcination, the decomposition of the spinnable polymer is incomplete, giving rise to the presence of residual carbon in the  $\text{ZrO}_2$  nanofiber, and this also reduces the mechanical properties of the microfiltration membrane.

To solve these problems, we attempt to prepare  $\text{SiO}_2$  nanofiber membranes by electrospinning and then obtain the  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes following impregnation. This approach will not produce a residual carbon in an oxygen-lacking atmosphere and was beneficial for increasing the positive charge on the membrane surface because the  $\text{ZrO}_2$  shell was impregnated without polymer additives. The obtained membranes also showed flexibility due to the characteristics of amorphous  $\text{SiO}_2$ . Effects of the impregnating solution content and the centrifugal speed on the morphologies, pore size and nanofiber diameter of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes were investigated and their phase composition, elemental valence state and the positive charge were characterized. Adsorption and separation properties of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes for titan yellow (simulating the negative charge of a virus) at different environmental conditions were also tested. The obtained membranes show prospects for broad applications in the fields of infectious virus protection, water treatment, pharmaceutical production and biological engineering.

## Experimental

### Materials and methods

Tetraethoxysilane (TEOS, AR, Tianjin Kermel Chemical Reagent Co., Ltd., Tianjin, China) and zirconium oxychloride (AR, Tianjin Guangfu Fine Chemical Research Institute, Tianjin, China) were used as Si and Zr precursors, respectively. Ethanol (AR, Anhui Ante Biochemical Co., Ltd., Suzhou, Anhui, China), *N,N*-dimethylformamide (AR, Tianjin Kermel Chemical Reagent Co., Ltd., Tianjin, China) and deionized water were used as solvents. Phosphoric acid (AR, Tianjin Yaohua chemical reagents Co., Ltd., Tianjin, China) was used as a hydrolysant for TEOS. Polyvinyl alcohol (PVA,  $M_w = 60\,000$ ) and polyvinylpyrrolidone (PVP,  $M_w = 1\,300\,000$ ) were purchased from Sigma Aldrich and used as spinnable polymers.

PVA was added to the deionized water at 70 °C to obtain the PVA solution by stirring for 6 h. TEOS was added to the deionized water and then the  $\text{SiO}_2$  solution was obtained by adding the phosphoric acid to hydrolyze the TEOS. The  $\text{SiO}_2$  solution was slowly added into the PVA solution to obtain the  $\text{SiO}_2$  spinning solution. The  $\text{SiO}_2$  spinning solution was loaded into a micropump, and PVA/ $\text{SiO}_2$  composite nanofibers were

obtained after electrospinning. Spinning parameters were as follows: spinning voltage of 20 kV, receiving distance of 15 cm, propulsion rate of 0.4 mL h<sup>-1</sup>, ambient temperature of 40 °C and relative humidity of 40%. Then, the PVA/ $\text{SiO}_2$  composite nanofibers were calcined for 2 h at 600 °C to obtain the  $\text{SiO}_2$  nanofibrous membranes. The impregnated solution was obtained by mixing  $\text{ZrOCl}_2$  in deionized water.  $\text{SiO}_2$  nanofibrous membranes were impregnated for 2 h and were centrifuged for 3 min to dry. Finally, coaxial  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes were obtained by calcination at 700 °C in vacuum or in 4% H<sub>2</sub>/96% N<sub>2</sub> mixed atmosphere for 2 h.

### Characterization

Morphologies of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes were characterized by SEM (JSM 6700F, JEOL, Japan) and using a stereo microscope (OLYMPUS, Tokyo, Japan). The pore size of the membranes and the diameter of the  $\text{SiO}_2@\text{ZrO}_2$  coaxial nanofibers were determined by Smile View (Software, JEOL, Japan) using SEM images; here, 50 pores and 50 nanofibers were tested in this manner to obtain the distribution and the average value. X-Ray diffraction (XRD; Model 7000, Shimadzu Corporation, Tokyo, Japan) was used to identify the phases in the membranes. The core/shell structure and the components of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibers were characterized by TEM (JEM-3010, JEOL, Japan). The specific surface areas of the nanofibrous membranes were characterized using a model BK122T-B analyzer by N<sub>2</sub> adsorption at -196 °C. The mechanical property of the nanofibrous membranes was tested with a fibers strength tester (LLY-06E, YuanMore, Shaoxing, China). The nanofibrous membranes were cut into rectangular pieces sized length × width = 10 mm × 4 mm (the thickness was about 0.6 mm). Tensile rate was 10 mm min<sup>-1</sup>. The zeta potential of  $\text{SiO}_2@\text{ZrO}_2$  nanofibers was determined using a microelectrophoresis instrument (JS94H, Shanghai zhongchen digital technology equipment Co. Ltd., China). Chemical compositions and binding energy of Zr 3d were analyzed by X-ray photoelectron spectroscopy (XPS, AXIS-ULTRA DLD, Shimadzu Corporation, Tokyo, Japan). Water flux was determined by a membrane flux meter (MF/UF, Hydra Netherlands); test parameters: effective filtration area of 12.56 cm<sup>2</sup>, thickness of 1 mm, operation pressure of 1 Pa. The adsorption and separation properties of the positively charged  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes were characterized using titan yellow (with 2 negative charges) as the simulated virus. The standard absorbance curve was obtained using a UV-visible spectrophotometer (UV-5100, METASH, China) using titan yellow solutions with different concentrations. The titan yellow solution (10 mg L<sup>-1</sup>) with different pH values was filtered using the  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes. The absorbance of the original solution and that of the filtered solution were determined, and the interception rate was calculated using eqn (1).

$$R = \left(1 - \frac{A_1}{A_2}\right) \times 100\% \quad (1)$$

where  $R$  is the interception rate,  $A_1$  is the absorbance of the original titan yellow solution, and  $A_2$  is the absorbance of the



filtered titan yellow solution. A 1 L titan yellow solution ( $10 \text{ mg L}^{-1}$ ) was filtered to determine the maximum adsorption capacity of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes.

## Results and discussion

### Morphologies and composites of electrospun $\text{SiO}_2@\text{ZrO}_2$ nanofibrous membranes

Impregnation was found to be an effective method for the preparation of coaxial nanofibers.<sup>24</sup>  $\text{ZrOCl}_2$  contents of the impregnating solutions had an important influence on the morphology of the nanofibrous membranes. Fig. 1 shows the morphologies of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes obtained by impregnating solutions with different contents. The centrifugal speed was 5000 rpm. The coaxial nanofiber after impregnation was still a long continuous nanofiber with a smooth surface. When the  $\text{ZrOCl}_2$  content of the impregnated solution increases to  $3 \text{ mol L}^{-1}$ , some adhesion occurred between the coaxial nanofibers. Some connections between the nanofibers were observed when the  $\text{ZrOCl}_2$  content reaches  $4 \text{ mol L}^{-1}$ . The impregnated solution was easily aggregated at the junction of the nanofibers due to the surface tension effect when the  $\text{ZrOCl}_2$  content increases, and it was difficult to remove it from the centrifuge, and the joint is formed at the lap of nanofibers after drying and sintering. However, this connection does not have a negative impact on the morphologies of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes in addition to a slight impact on the surface area.  $\text{ZrOCl}$  was adsorbed on the surface of  $\text{SiO}_2$  when impregnating, and the  $\text{ZrO}_2$  shell can finally be formed in the oxygen-lacking atmosphere.

Pore size distributions of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes and diameters distribution of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibers were characterized, as shown in Fig. 2. With the increase of the  $\text{ZrOCl}_2$  contents of the impregnated solutions, the average pore size of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes decreased from 756.2 nm to 721.2 nm, but the main distribution range of the pore size did not change, which is closely related to the diameter of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibers. The

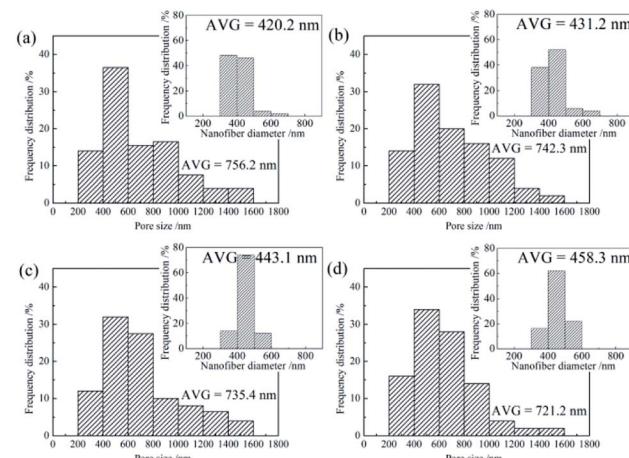


Fig. 2 Pore size distributions of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes obtained by impregnating solutions with different  $\text{ZrOCl}_2$  contents: (a) 1; (b) 2; (c) 3; (d) 4  $\text{mol L}^{-1}$ .

average diameter of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibers increased from 420.2 nm to 458.3 nm with the increase of the  $\text{ZrOCl}_2$  content, and the number of the nanofibers between 300 and 400 nm decreased significantly (images in insets of Fig. 2). This is mainly because the increase in the  $\text{ZrOCl}_2$  content can increase the thickness of the  $\text{ZrO}_2$  shell. The increase of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibers diameter leads to the decrease of the pore size of the nanofibrous membranes.

Fig. 3 shows the macro morphology of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes. The  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membrane shows excellent flexibility and can bend to form a O shape with the diameter of 10 mm. This flexibility is mainly due to the character of the  $\text{SiO}_2$  core. The  $\text{SiO}_2$  core of the coaxial nanofibers is amorphous and is mainly connected by an infinite  $\text{SiO}_4$  tetrahedral network. Since the size of the core is very small, the volume percentage of the  $\text{SiO}_2$  internal boundary increases, which means that more atoms can be assigned to the boundary.<sup>25,26</sup> Therefore, a large reduction in the stress concentration reduces the extension of micro-cracks on the  $\text{SiO}_2$  nanofiber. Although the shell consists of brittle  $\text{ZrO}_2$ ,

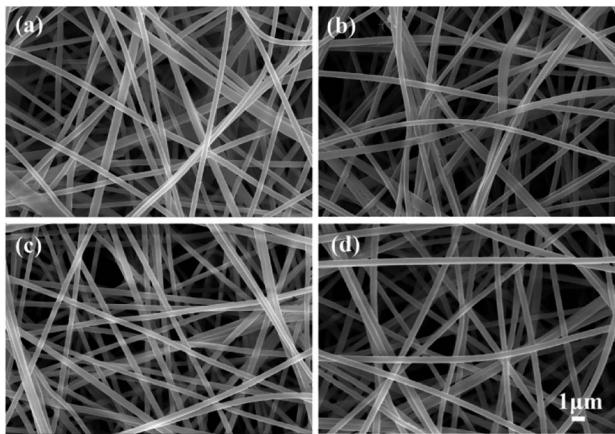


Fig. 1 Morphologies of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes obtained by impregnating solutions with different  $\text{ZrOCl}_2$  contents: (a) 1; (b) 2; (c) 3; (d) 4  $\text{mol L}^{-1}$ .

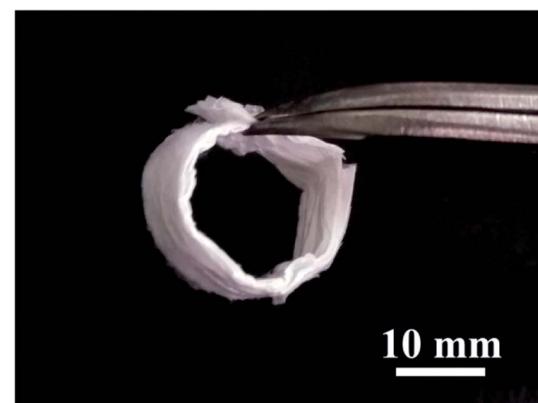


Fig. 3 Macro morphology of flexible  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes.



$\text{SiO}_2@\text{ZrO}_2$  nanofiber shows flexibility because of its small thickness, which is beneficial to the stability of filtration.

Fig. 4 shows the XRD patterns of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes. The diffraction peak of  $\text{SiO}_2$  was not found because the  $\text{SiO}_2$  obtained by electrospinning usually was amorphous. Strong diffraction peaks of the membranes coincided with the characteristic peaks of the  $(\bar{1}11)$ ,  $(111)$  and  $(220)$  planes in the monoclinic  $\text{ZrO}_2$  (JCPDS 37-1484). Some weak diffraction peaks coincided with the  $(101)$ ,  $(002)$  and  $(200)$  characteristic peaks in the tetragonal  $\text{ZrO}_2$  (JCPDS 42-1164). The  $\text{ZrO}_2$  shell of the coaxial nanofibers was mainly found in the monoclinic phase and contains a small amount of tetragonal phase.

The microstructure and composition of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes were further characterized by XPS, as shown in Fig. 5. Fig. 5(a) shows the TEM micrograph of the  $\text{SiO}_2@\text{ZrO}_2$  nanofiber. The obvious coaxial structure was observed. The black part was the core of the coaxial nanofiber, which is a  $\text{SiO}_2$  nanofiber obtained by electrospinning. The light gray region was the  $\text{ZrO}_2$  shell of the coaxial nanofiber, with the thickness of approximately 10–30 nm. In the HRTEM micrograph of the  $\text{SiO}_2@\text{ZrO}_2$  nanofiber (Fig. 5(b)), the dark region was amorphous and was speculated to be amorphous  $\text{SiO}_2$ . The interplanar spacing of the light-colored shell was 0.316 nm, corresponding to the  $(\bar{1}11)$  plane of monoclinic- $\text{ZrO}_2$  and indicating that the  $\text{ZrO}_2$  shell was mainly found in the monoclinic phase. The  $\text{ZrO}_2$  shell was further amplified, as shown in Fig. 5(c). It can be observed that the grain size of  $\text{ZrO}_2$  was about 15 nm.

### Specific surface area and water flux of $\text{SiO}_2@\text{ZrO}_2$ nanofibrous membranes

Fig. 6 shows the water fluxes and specific surface areas of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes with different average pore sizes. With the increase of the pore size of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes, the water flux decreases, and the specific surface area decreases. When the average pore size was 768.2 nm, the maximum water flux was 643.1  $\text{L}(\text{m}^2 \text{h})^{-1}$  and the specific surface area was 265.1  $\text{m}^2 \text{g}^{-1}$ , which is mainly related

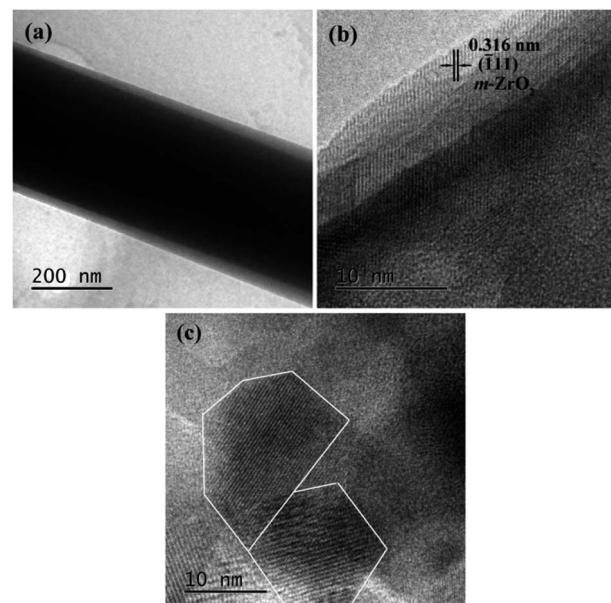


Fig. 5 (a) TEM micrograph of the  $\text{SiO}_2@\text{ZrO}_2$  nanofiber; (b) HRTEM micrograph of the  $\text{SiO}_2@\text{ZrO}_2$  nanofiber; (c) magnification of (b).

to the diameter of  $\text{SiO}_2@\text{ZrO}_2$  nanofibers. Together with the results presented in Fig. 1, this shows that the large pore size of the nanofibrous membranes was obtained by a small nanofiber diameter, which is beneficial for the solution flow through the membrane. Meanwhile, the specific surface area also reached the maximum value, which can improve the filtration efficiency and adsorption capacity of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes.

In practical use, the positive charged  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes should be mechanically strong enough to bear the water flux. The tensile strength of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes was tested and the stress-strain curve was shown in Fig. 7. With the increase of the applied tensile strain, the  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membrane broke in a mild style. The tensile strength was 0.24 MPa, which was higher than that of the  $\text{SiO}_2$  filtration film reported in the literature.<sup>27</sup>

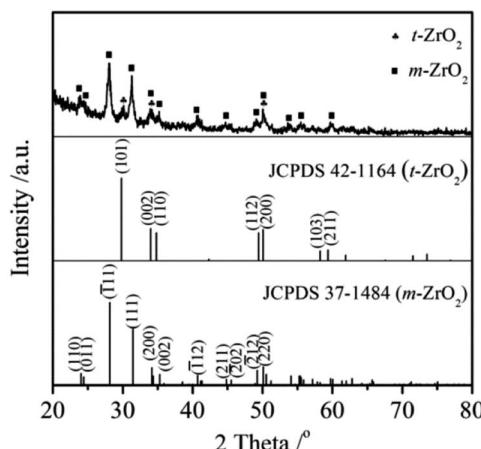


Fig. 4 XRD patterns of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes.

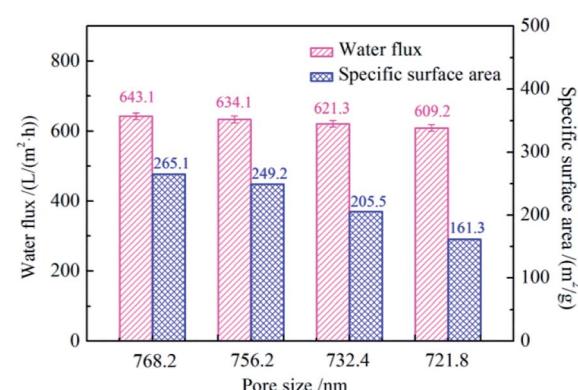


Fig. 6 Water fluxes and specific surface areas of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes with different average pore sizes.



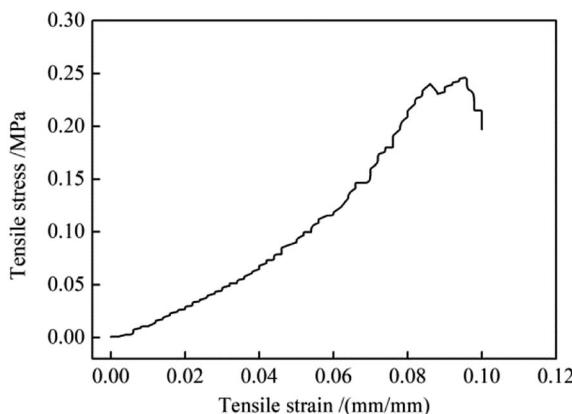


Fig. 7 Stress-strain curve of  $\text{SiO}_2@ZrO_2$  nanofibrous membranes with the pore size of 768.2 nm.

### Positive charged properties of $\text{SiO}_2@ZrO_2$ nanofibrous membranes

The  $\text{SiO}_2@ZrO_2$  nanofibrous membrane with the largest water flux and specific surface area was selected for the testing of its surface zeta potential under different pH, and the results for the samples with the calcination performed in different atmospheres were compared, as shown in Fig. 8. The surface zeta potentials of  $\text{SiO}_2@ZrO_2$  nanofibrous membranes calcined in air, vacuum and in 96%  $\text{N}_2/4\% \text{H}_2$  atmosphere decrease with increasing pH. Zeta potentials of the calcined nanofibrous membranes in the mixed atmosphere were slightly higher than that of the vacuum calcined nanofibrous membranes. The isoelectric point (IEP) of the  $\text{SiO}_2@ZrO_2$  nanofibrous membranes after calcination at vacuum was 7.1, and the IEP was 7.4 after calcination of 96%  $\text{N}_2/4\% \text{H}_2$ , which is much larger than and the IEP (4.5) of that calcined in air and also the IEP of  $\text{ZrO}_2$  nanofiber membrane.<sup>23</sup> The IEP of the  $\text{SiO}_2@ZrO_2$  nanofibrous membranes can be obviously increased by calcining in 96%  $\text{N}_2/4\% \text{H}_2$  mixture atmosphere, because the oxygen vacancy concentration of  $\text{ZrO}_2$  surface can be increased, resulting in the IEP shifting to the right.

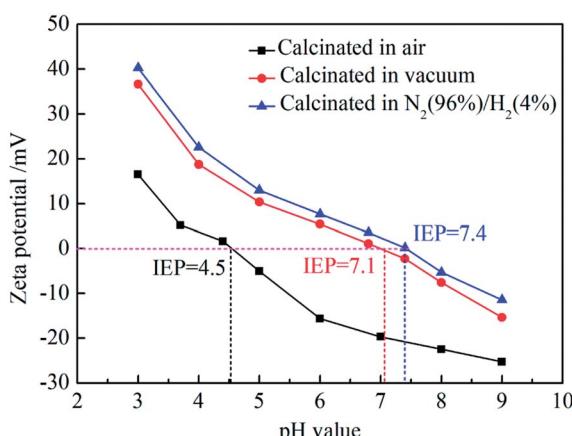


Fig. 8 Zeta potentials of surfaces on  $\text{SiO}_2@ZrO_2$  nanofibrous membranes in solutions with different pH values.

To further analyze the  $\text{ZrO}_2$  oxygen vacancies in the  $\text{SiO}_2@ZrO_2$  nanofibrous membranes, XPS was used to perform elemental analysis and the peak fitting of the Zr element was carried out in detail, as shown in Fig. 9. Fig. 9(a) shows full spectrum of the positively charged  $\text{SiO}_2@ZrO_2$  nanofibrous membranes calcined in vacuum and in 96%  $\text{N}_2/4\% \text{H}_2$  mixture. The components of the  $\text{SiO}_2@ZrO_2$  nanofibrous membranes were Zr, Si and O (C was the calibrated element). Fig. 9(b) shows the peak fitting curves of the Zr 3d fine spectrum. Electron binding energies of Zr 3d $5/2$  in the  $\text{ZrO}_2$  shell of vacuum-calcined nanofibrous membranes were 182.8 and 180.9 eV (electron binding energies of 3d $3/2$  were 180.4 and 179.5 eV), corresponding to  $\text{ZrO}_2$  and  $\text{ZrO}_x$  ( $0 < x < 2$ ),<sup>28,29</sup> respectively. This indicates that the surface of the  $\text{SiO}_2@ZrO_2$  nanofibrous membranes contains oxygen vacancies. The binding energy of Zr in the  $\text{ZrO}_2$  shell of nanofibrous membranes after calcining in 96%  $\text{N}_2/4\% \text{H}_2$  mixture atmosphere still corresponded to  $\text{ZrO}_2$  and  $\text{ZrO}_x$  ( $0 < x < 2$ ), respectively. The increase of  $\text{ZrO}_x$  content indicates that the number of oxygen vacancies on the surface of the fiber increases after the calcining of the 96%  $\text{N}_2/4\% \text{H}_2$  mixture atmosphere. A higher oxygen vacancy content gives rise to the increased zeta positive potential of the  $\text{SiO}_2@ZrO_2$  nanofibrous membrane and increases the positive charge on

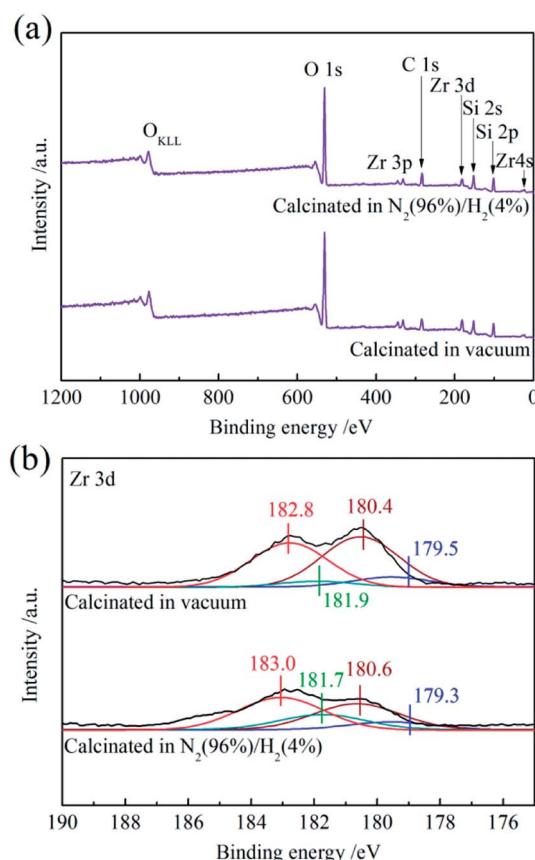


Fig. 9 XPS spectra of positively charged  $\text{SiO}_2@ZrO_2$  nanofibrous membranes calcined in vacuum and  $\text{N}_2$  (96%)/ $\text{H}_2$  (4%) mixture: (a) full spectrum and (b) Zr 3d.



the nanofiber surface. According to XRD analysis,  $\text{ZrO}_2$  was mainly in the monoclinic phase, but some tetragonal phases were present as well, which may be related to the existence of oxygen vacancies. It is generally believed that the existence of the tetragonal phase in the oxygen-lacking conditions is due to the oxygen vacancies.<sup>30</sup> The surface of the sample may form a structure with an oxygen vacancy distortion, which can prevent the transformation from the monoclinic phase to the tetragonal phase.<sup>31</sup> Despite the exposure to air, the transformation of the tetragonal phase into the monoclinic phase still takes a long time due to the instability of the surface.

### Adsorption and separation properties of positive charged $\text{SiO}_2@\text{ZrO}_2$ nanofibrous membranes

The separation of positively charged  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes for electrical neutral materials was mainly due the physical sieving effect, and there is an electrostatic adsorption between the negatively charged material on the positively charged membrane.<sup>32</sup> The titan yellow with two negative charges was used to characterize the separation property of the positively charged  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes. The charged fiber membrane was electrically neutral with no charge at the IEP. When the pH value was less than the IEP, titan yellow was separated by the adsorption on the positively charged nanofibrous membranes. Fig. 10 shows the interception rates of the positively charged  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes for a titan yellow solution at different pH values. The interception rate of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes calcined in air was 99.99% in titan yellow solution with pH = 3–3.5. The interception rate decreased rapidly at pH > 3.5, and was only 0.06% at pH = 9. The interception rate of the vacuum-calcined  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes in the solution with pH value from 3 to 6.5 remains above 99.996%. The interception rate decreased rapidly when the pH value of the solution was greater than 6.5, because the positively charge of the surface decreases and the interception mechanism for titan yellow was physical only. The titan yellow can pass through  $\text{SiO}_2@\text{ZrO}_2$

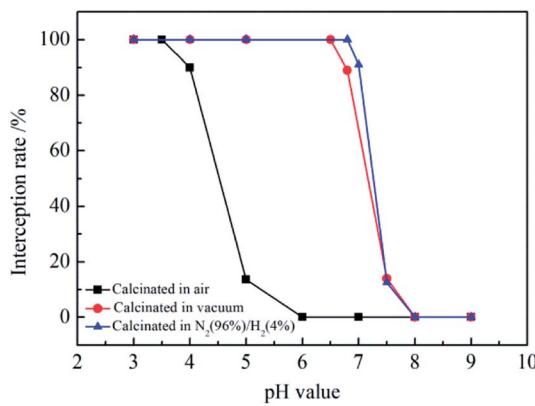


Fig. 10 Interception rates of positively charged  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes calcined in air, vacuum and  $\text{N}_2$  (96%)/ $\text{H}_2$  (4%) mixture for titan yellow solution for different pH values.

nanofibrous membranes under pressure, so that the interception rate was very low. The interception rate of 96%  $\text{N}_2$ /4%  $\text{H}_2$  mixture atmosphere calcined nanofibrous membranes was consistent with that of the vacuum-calcined nanofibrous membranes. However, the interception rate for titan yellow was higher than that of the vacuum-calcined nanofibrous membranes for the pH value of the solution in the 6.5–7.5 range. The interception rate was closely related to the positive charge of the nanofiber surface. The greater the positive charge, the higher the interception rate for the pH value smaller than the IEP.

Fig. 11 shows the adsorption capacities of the positively charged  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes for a titan yellow solution at different pH. Adsorption capacity of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes calcined in air were observed when the pH was lower than 4. When pH was higher than 6, the adsorption capacity was 0. The saturation adsorption capacity of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes calcined in vacuum and  $\text{N}_2$  (96%)/ $\text{H}_2$  (4%) mixture at pH = 3–6.5 was reached, and the maximum saturated adsorption capacity was 64.36 mg  $\text{cm}^{-3}$ . When the pH was higher than 6.5, the saturation adsorption capacity rapidly decreases, and reaches the minimum value of only approximately 0.03 mg  $\text{cm}^{-3}$  for pH 8. Adsorption capacities of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes calcinated in the  $\text{N}_2$  (96%)/ $\text{H}_2$  (4%) mixture atmosphere and vacuum were basically the same. The  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes surface has a strong positive charge in the solution with the pH lower than the IEP, so that the membrane can intercept the titan yellow molecules by electrostatic adsorption. When the pH of the solution was above the IEP, the saturated adsorption capacity of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes decreased rapidly due the absence of adsorption for the membrane surface with a negative charge. Nanofibrous membranes can only intercept a small amount of titan yellow by the mechanism of physical interception. Thus, higher pH corresponds to greater electronegativity and lower adsorption capacity.

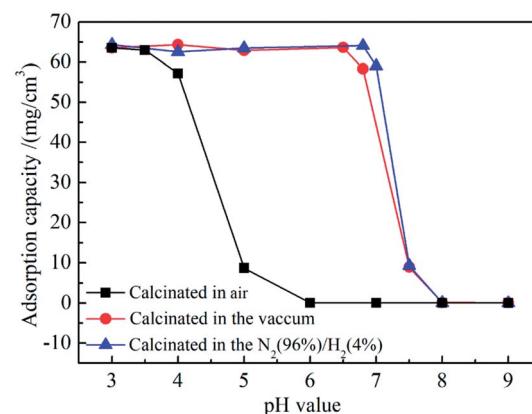


Fig. 11 Adsorption capacities of positively charged  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes calcined in air, vacuum and  $\text{N}_2$  (96%)/ $\text{H}_2$  (4%) mixture for titan yellow solution at different pH.



## Conclusions

$\text{SiO}_2@\text{ZrO}_2$  coaxial nanofibrous membranes were prepared by electrospinning and impregnation in oxygen-lacking atmospheres. The resulting nanofibrous membranes show excellent flexibility. The maximum specific surface area of the  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membrane with the pore size in 721.8–768.2 nm range can reach  $249.24 \text{ m}^2 \text{ g}^{-1}$ , and the maximum water flux was  $643.1 \text{ L} (\text{m}^2 \text{ h})^{-1}$ .  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes obtained by calcining in oxygen-lack atmosphere consist of a monoclinic phase and a small amount of a tetragonal phase. Oxygen vacancies were found on their surface, and Zr is found in a low oxidation state. Calcining in the 96%  $\text{N}_2$ /4%  $\text{H}_2$  mixture atmosphere can improve the IEP of the membrane to 7.3. The maximum water flux of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes was  $643 \text{ L} (\text{m}^2 \text{ h})^{-1}$  when the effective filtration area was  $12.56 \text{ cm}^2$ , the membrane thickness was 1 mm and the operating pressure was 1 Pa. Furthermore, the interception rate of the 96%  $\text{N}_2$ /4%  $\text{H}_2$  mixture atmosphere calcined membrane for 20 mL titan yellow solution with the concentration of  $10 \text{ mg L}^{-1}$  reached 99.996% for the pH of less than 6.7. The saturated adsorption capacity reached  $63.27 \text{ mg cm}^{-3}$  for the filtration of 1 L titan yellow solution. The adsorption and separation of  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes calcined in the 96%  $\text{N}_2$ /4%  $\text{H}_2$  mixture atmosphere were greater than those in air and vacuum, which is mainly due to the increase of the surface oxygen vacancies and the positive surface charge. These positively charged  $\text{SiO}_2@\text{ZrO}_2$  nanofibrous membranes utilize physical separation and electrostatic adsorption to effectively remove negatively charged particles; this outcome has potential application in the separation of bacteria and viruses from water. However, nanofibrous membranes with the excellent adsorption and separation properties in water with pH between 5 and 9 need to be obtained by increasing the IEP, meeting the requirements of the Environmental Protection Agency for virus filters. This is still the main direction of future experiments.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors would like to acknowledge the support from the National Natural Science Foundation of China (No. 51572217), the China Postdoctoral Science Foundation (No. 2015M582689) and the Postdoctoral Science Foundation of Shaanxi Province (No. 2016BSHEDZZ03).

## References

- 1 H. van der Laan, D. van Halem, P. W. M. H. Smeets, A. I. A. Soppe, J. Kroesbergen, G. Wubbels, J. Nederstigt, I. Gensburger and S. G. J. Heijman, Bacteria and virus removal effectiveness of ceramic pot filters with different silver applications in a long term experiment, *Water Res.*, 2014, **51**, 47–54.
- 2 N. Shirasaki, T. Matsushita, Y. Matsui, M. Kobuke and K. Ohno, Comparison of removal performance of two surrogates for pathogenic waterborne viruses, bacteriophage Q $\beta$  and MS2, in a coagulation-ceramic microfiltration system, *J. Membr. Sci.*, 2009, **326**, 564–571.
- 3 Y. Kamato and Y. Suzuki, Reactively sintered porous  $\text{MgAl}_2\text{O}_4$ , for water-purification filter with controlled particle morphology, *Ceram. Int.*, 2017, **43**, 14090–14095.
- 4 M. Sarro, N. P. Gule, E. Laurenti, R. Gamberini, M. C. Paganini, P. E. Mallon and P. Calza, Freeze casting of novel porous silicate cement supports using tert-butyl alcohol-water binary crystals as template: Microstructure, strength and permeability, *J. Membr. Sci.*, 2017, **541**, 143–152.
- 5 N. Kouras, A. Harabi, F. Bouzerara, L. Foughali, A. Policicchio, S. Stelitano, F. Galiano and A. Figoli, Macro-porous ceramic supports for membranes prepared from quartz sand and calcite mixtures, *J. Eur. Ceram. Soc.*, 2017, **37**, 3159–3165.
- 6 Y. Lv, H. Liu, Z. Wang, S. Liu, L. Hao, Y. Sang, D. Liu, J. Wang and R. I. Boughton, Silver nanoparticle-decorated porous ceramic composite for water treatment, *J. Membr. Sci.*, 2009, **331**, 50–56.
- 7 S. Barg, D. Koch and G. Grathwohl, Processing and properties of graded ceramic filters, *J. Am. Ceram. Soc.*, 2009, **92**, 2854–2860.
- 8 J. Gröttrup, F. Schütt, D. Smazna, O. Lupon, R. Adelung and Y. K. Mishra, Porous ceramics based on hybrid inorganic tetrapodal networks for efficient photocatalysis and water purification, *Ceram. Int.*, 2017, **43**, 14915–14922.
- 9 C. R. Bowen and T. Thomas, Macro-porous  $\text{Ti}_2\text{AlC}$  MAX-phase ceramics by the foam replication method, *Ceram. Int.*, 2015, **41**, 12178–12185.
- 10 S. Deville, E. Saiz and A. P. Tomsia, Ice-templated porous alumina structures, *Acta Mater.*, 2007, **55**, 1965–1974.
- 11 Y. Tang, S. Qiu, C. Wu, Q. Miao and K. Zhao, Freeze cast fabrication of porous ceramics using tert-butyl alcohol-water crystals as template, *J. Eur. Ceram. Soc.*, 2016, **36**, 1513–1518.
- 12 R. Sondhi, Y. S. Lin and F. Alvarez, Crossflow filtration of chromium hydroxide suspension by ceramic membranes: fouling and its minimization by backpulsing, *J. Membr. Sci.*, 2000, **174**, 111–122.
- 13 Y. Tang, M. Mao, S. Qiu and K. Zhao, Fabrication of porous ceramics with double-pore structure by stepwise freeze casting using water/diphenyl methane emulsion, *Ceram. Int.*, 2018, **44**, 1187–1192.
- 14 J. Maurath, J. Dittmann, N. Schultz and N. Willenbacher, Fabrication of highly porous glass filters using capillary suspension processing, *Sep. Purif. Technol.*, 2015, **149**, 470–478.
- 15 H. Fong and D. H. Reneker, Electrospinning and formation of nanofibers in *Structure formation in polymeric fibers*, ed. D. R. Salem, Hanser Publishers, Munich, 2001, pp. 225–246.
- 16 M. Bognitzki, W. Czado, T. Frese, A. Schaper, M. Hellwig, M. Steinhart, A. Greiner and J. H. Wendorff, Nanostructured fibers via electrospinning, *Adv. Mater.*, 2001, **13**, 70–72.



- 17 M. Sarro, N. P. Gule, E. Laurenti, R. Gamberini, M. C. Paganini, P. E. Mallon and P. Calza, ZnO-based materials and enzymes hybrid systems as highly efficient catalysts for recalcitrant pollutants abatement, *Chem. Eng. J.*, 2018, **334**, 2530–2538.
- 18 S. Zhan, D. Chen, X. Jiao and Y. Song, Mesoporous TiO<sub>2</sub>/SiO<sub>2</sub> composite nanofibers with selective photocatalytic properties, *Chem. Commun.*, 2007, **20**, 2043–2045.
- 19 R. Allabashi, M. Arkas, G. Hörmann and D. Tsiorvas, Removal of some organic pollutants in water employing ceramic membranes impregnated with cross-linked silylated dendritic and cyclodextrin polymers, *Water Res.*, 2007, **41**, 476–486.
- 20 S. Abbasizadeh, A. R. Keshtkar and M. A. Mousavian, Preparation of a novel electrospun polyvinyl alcohol/titanium oxide nanofiber adsorbent modified with mercapto groups for uranium(vi) and thorium(iv) removal from aqueous solution, *Chem. Eng. J.*, 2013, **220**, 161–171.
- 21 B. L. T. Lau, G. W. Harrington, M. A. Anderson and I. Tejedor, Removal of nano and microparticles by granular filter media coated with nanoporous aluminium oxide, *Water Sci. Technol.*, 2004, **20**, 223–228.
- 22 M. Wegmann, B. Michen, T. Luxbacher, J. Fritsch and T. Graule, Modification of ceramic microfilters with colloidal zirconia to promote the adsorption of viruses from water, *Water Res.*, 2008, **429**, 1726–1734.
- 23 Y. Tang, Z. Liu, K. Zhao and S. Fu, Adsorption and separation properties of positively charged ZrO<sub>2</sub> nanofibrous membranes fabricated by electrospinning, *RSC Adv.*, 2017, **7**, 42505–42512.
- 24 C. H. Park, C. H. Kim, L. D. Tijing, D. H. Lee, M. H. Yu, H. R. Pant, Y. Kim and C. S. Kim, Preparation and characterization of (polyurethane/nylon-6) nanofiber/(silicone) film composites *via* electrospinning and dip-coating, *Fibers Polym.*, 2012, **13**, 339–345.
- 25 M. Guo, B. Ding, X. Li, X. Wang, J. Yu and M. Wang, Amphiphobic nanofibrous silica mats with flexible and high-heat-resistant properties, *J. Phys. Chem. C*, 2010, **114**, 916–921.
- 26 X. Wang, L. Dou, L. Yang, J. Yu and B. Ding, Hierarchical structured MnO<sub>2</sub>@SiO<sub>2</sub>, nanofibrous membranes with superb flexibility and enhanced catalytic performance, *J. Hazard. Mater.*, 2017, **324**, 203–212.
- 27 Z. Ma, Z. Hu, X. He, Z. Fang, Y. Li and J. Qiu, Nano-Bi<sub>2</sub>WO<sub>6</sub> functionalized flexible SiO<sub>2</sub> fibrous film for water purification, *Appl. Surf. Sci.*, 2016, **360**, 174–183.
- 28 P. C. Wong, Y. S. Li, M. Y. Zhou and K. A. R. Mitchell, XPS investigations of the interactions of hydrogen with thin films of zirconium oxide I. Hydrogen treatments on a 10 Å thick film, *Appl. Surf. Sci.*, 1995, **89**, 255–261.
- 29 Y. S. Li, P. C. Wong and K. A. R. Mitchell, XPS investigations of the interactions of hydrogen with thin films of zirconium oxide II. Effects of heating a 26 Å thick film after treatment with a hydrogen plasma, *Appl. Surf. Sci.*, 1995, **89**, 263–269.
- 30 R. Srinivasan, C. R. Hubbard, O. B. Cavin and B. H. Davis, Factors determining the crystal phases of zirconia powers - A new outlook, *Chem. Mater.*, 1993, **5**, 27–31.
- 31 W. Z. Zhu and M. Yan, Stability of tetragonal phase in ZrO<sub>2</sub> (2 mol% Y<sub>2</sub>O<sub>3</sub>) ceramics sintered in reducing atmosphere, *J. Mater. Sci. Lett.*, 1997, **16**, 1540–1543.
- 32 M. Wegmann, B. Michen and T. Graule, Nanostructured surface modification of microporous ceramics for efficient virus filtration, *J. Eur. Ceram. Soc.*, 2008, **28**, 1603–1612.

