



Cite this: *Chem. Soc. Rev.*, 2025, 54, 6062

Design and structure–function interplay in covalent organic frameworks for photocatalytic CO₂ reduction

Shibani Mohata, ^{a,b} Poulami Majumder ^{ab} and Rahul Banerjee ^{abc}

The escalating global energy demands and the need to alleviate the rapid rise in greenhouse gases have led to colossal interest in designing efficient catalytic systems for photocatalytic CO₂ reduction. While inorganic semiconductors have been the frontrunners for a long time, porous photocatalysts, particularly covalent organic frameworks (COFs), are gaining traction due to their atomically precise structures, enabling tuning their structural and chemical properties. Designed using the principles of reticular chemistry, the building units of COFs can be modulated to incorporate catalytically active sites periodically using robust covalent bonds to endow them with high efficiency, selectivity, and stability. Unlike the non-porous congeners, COFs, with their high porosity and precisely defined pore channels, allow for quicker diffusion of substrates and products, enabling the utilization of deeply buried photocatalytic sites. Our approach is to comprehend the significant roadblocks that must be overcome for designing state-of-the-art catalysts for photocatalytic CO₂ reduction. Building upon that, we highlight the key strategies devised to design COF-based CO₂RR photocatalysts. A fundamental understanding of the structure–property relationship is quintessential for utilizing the precision of COF chemistry for developing next-generation materials combining activity, selectivity, and efficiency in a single system. Throughout this review, we have taken a closer look at how the critical design aspects and molecular engineering reciprocate towards augmenting the bulk photocatalytic properties of efficiency and selectivity. Understanding molecular engineering and structure–property relationships will be conducive to developing sophisticated systems to solve global crises in this burgeoning area of research.

Received 24th February 2025

DOI: 10.1039/d5cs00106d

rsc.li/chem-soc-rev

^a Department of Chemical Sciences, Indian Institute of Science Education and Research, Kolkata, Mohanpur 741246, India. E-mail: shibanimohata@gmail.com, r.banerjee@iiserkol.ac.in

^b Centre for Advanced Functional Materials, Indian Institute of Science Education and Research, Kolkata 741246, India

^c College of Science, Korea University, 145 Anam-ro Seongbuk-gu, South Korea



Shibani Mohata

Dr Shibani Mohata received her PhD degree from the Department of Chemical Sciences, Indian Institute of Science Education and Research (IISER) Kolkata, India, in September 2024, under the supervision of Prof. Rahul Banerjee. She completed her BSc degree at SKBU University and received her MS degree from IISER Kolkata, India. Her research focuses on the design and synthesis of organic porous materials, 2D covalent organic framework membranes, and their applications in the development of heterogeneous photocatalytic CO₂ reduction catalysts.

branched, and their applications in the development of heterogeneous photocatalytic CO₂ reduction catalysts.



Poulami Majumder

Dr Poulami Majumder completed her PhD in the Department of Chemical Sciences, Indian Institute of Science Education and Research (IISER) Kolkata, India, under the supervision of Prof. Rahul Banerjee. She completed her BSc degree at Burdwan University and received her MSc degree from the Indian Institute of Science Education and Research (IISER) Kolkata, India. Her research interest is in exploring heterogeneous photocatalysis by using the covalent organic framework.



1. Introduction

The industrial revolution has led to a drastic increase in CO₂ emissions from various anthropogenic sources, disrupting the carbon cycle.¹ CO₂ reduction to value-added products is an attractive route to mitigate this environmental crisis and achieve the coveted carbon-neutral economy.² This has led to colossal interest in developing efficient catalytic processes and systems. Among the primary strategies for CO₂ reduction, the most prominent include (a) electrocatalysis, (b) thermocatalysis, (c) biocatalysis, and (d) photocatalysis.^{3–5} While highly efficient and selective, biological catalysts are inherently fragile and constrained by stringent operational conditions, such as specific temperature and pH requirements.⁶ Thermocatalysis has demonstrated considerable progress; however, it typically necessitates elevated temperatures (≥ 500 K) and high pressures (≥ 10 atm).⁷ Electrocatalysis, a widely studied alternative, offers high efficiency but relies heavily on external electricity sources, rendering the process less sustainable and economically viable.^{8,9} In this regard, photocatalytic CO₂ reduction has come to the forefront as a method to develop greener, cost-effective, and more sustainable approaches to advance the field of CO₂ reduction. Compared to the conventional methods, photocatalytic transformation bestows several advantages: (1) it can be achieved at ambient temperatures and pressures, (2) using renewable (sun) light energy and comparatively simplistic reactors, and most importantly, (3) it can generate chemical fuels using only water and CO₂ as feeds without introducing secondary pollution.^{10,11}

Designing an efficient photocatalyst with high activity and selectivity necessitates meeting specific criteria. The photocatalyst should possess a high density of exposed active sites to facilitate reactions, exhibit structural robustness to endure multiple catalytic cycles and maintain a well-defined structure to clearly understand structure–property relationships.^{12,13} The catalyst should be tunable to accommodate varying application requirements, ensuring versatility and optimization for specific

processes.¹⁴ Covalent organic frameworks (COFs) serve as ideal platforms for achieving this within a single system.^{15–19} They are bestowed with periodic structures with abundant active sites, high surface areas, and well-defined pore channels conducive to facile diffusion of substrates to the active sites, resulting in high catalytic activity. Reticular chemistry enables the selection of tailored building units inspired by selective molecular catalysts, imparting them with high selectivity.^{20,21} Their extended structures render them insoluble in most common organic solvents, ensuring easy isolation through centrifugation. Moreover, these strong covalent linkages provide remarkable stability, allowing the materials to be reused across several reaction cycles. Significant efforts have been made to optimize the optoelectronic properties of COFs in terms of the light harnessing capability, charge separation and transfer, and band positions, imparting high photocatalytic efficiency.^{22–24} Although great strides have been made in developing COF-based catalysts for photocatalytic CO₂ reduction, a gap persists in understanding the structure–property relationship and how the catalytic performance correlates with their molecular architecture.

This review delves into the intriguing research on engineering covalent organic frameworks for photocatalytic CO₂ reduction. We highlight the diverse porous materials established as outstanding platforms for a broad spectrum of photocatalytic applications, with particular emphasis on the fundamental mechanisms of COFs in photocatalysis. A special focus has been placed on understanding the challenges associated with developing an ideal catalyst for photocatalytic CO₂ reduction. We have emphasized the need to tackle key challenges, including improving product selectivity, mitigating parasitic hydrogen evolution in water, reducing dependence on metals, enhancing the oxidation half-reaction, addressing product overestimation, and preventing catalyst decomposition. We identify the properties of porous materials that set them apart from other semiconductor photocatalysts as promising materials for photocatalysis. Our discourse extends to the various strategies developed to design covalent organic frameworks for photocatalytic CO₂ reduction reactions. COF-based photocatalysts are divided into two subclasses: (i) metalated: COFs bearing metal centres that act as active sites for CO₂ reduction, enhancing catalytic efficiency and (ii) metal-free: systems relying on organic components to facilitate CO₂ reduction. Ideally, such systems should also be free of metal-based photosensitizers or co-catalysts. We have extensively discussed the various important developments in these two classes. Our approach focuses on understanding the fundamental structure–function relationship to determine catalyst efficiency and selectivity. Developing a thorough understanding of the design principles affecting the photophysical and physiochemical properties of COFs will open new avenues for future research on developing tailor-made photocatalysts for CO₂ reduction.



Rahul Banerjee

Prof. Rahul Banerjee has been a professor at IISER Kolkata since 2017. His research interests include crystallography, reticular chemistry and organic material synthesis. His group has developed unique methodologies of synthesizing covalent organic frameworks with various morphologies and exceptional chemical stability. His group further utilized the covalent organic frameworks (COFs) for carbon sequestration, water purification, energy storage and conversion, and separation applications. He has published more than 180 research articles, which have attracted 37 900+ citations with an h-index of 92.

This journal is © The Royal Society of Chemistry 2025

2. Porous photocatalysts and their applications

Photocatalysis has emerged as a greener and more cost-effective alternative, leveraging renewable solar energy under ambient



temperature and pressure conditions while minimizing secondary pollution. This advancement has spurred the development of various homogeneous and heterogeneous semiconductor photocatalysts, including metals (*e.g.*, Cu, Au, and Ag), titanium dioxide, molecular transition-metal complexes, metal oxides and chalcogenides, perovskites, and MXenes.^{25–30} Despite their promise, these materials face challenges such as limited band gap tunability, restricted light absorption, reliance on expensive noble metals, and surface deactivation. Additionally, their low porosity confines reactions to surface-exposed sites, thereby reducing efficiency.

Homogeneous photocatalysts are widely studied for their well-defined chemical structures and the ability to fine-tune their activity by modifying ligands, metals, and coordination spheres, providing fundamental insights into reaction mechanisms.^{31,32} Conversely, heterogeneous photocatalysts, while

more challenging to characterize in terms of active sites or intermediates, offer advantages such as higher activity, stability, and recyclability.^{33,34}

In this context, porous materials engineered through the principles of reticular chemistry bridge the gap between these approaches.³⁵ Their high surface area and tunable pore environments facilitate efficient mass transport, charge transfer, and accessibility to active sites.³⁶ These features significantly enhance the efficiency and selectivity of photochemical transformations, providing an optimal blend of functionality and performance.

Porous materials span from zero-dimensional molecular cages and one-dimensional nanotubes to two and three-dimensional metal-organic frameworks (MOFs), covalent organic frameworks (COFs), and hydrogen-bonded frameworks (HOFs) (Fig. 1a).^{37,38} They differ based on their crystallinity and

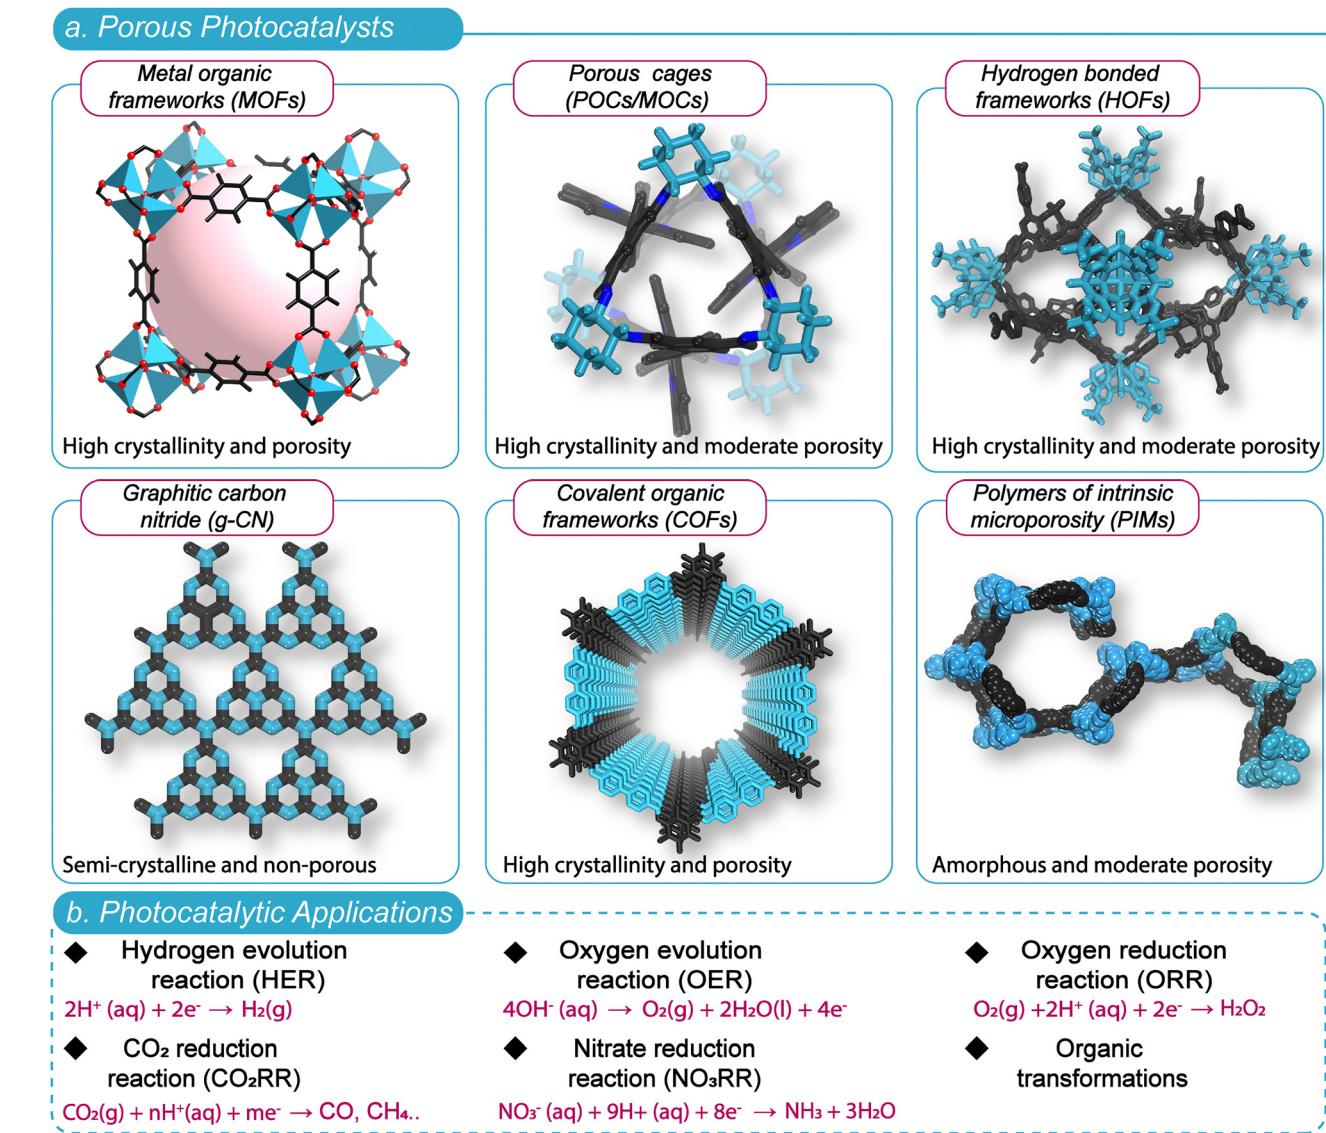


Fig. 1 (a) Schematic representation of the various categories of porous heterogeneous photocatalysts constructed using precise building units. (b) Illustration of the different photocatalytic applications of porous materials.



porosity, based on which they can be categorized as amorphous with ill-defined structures like polymers of intrinsic micro-porosity (PIMs) and crystalline with well-ordered structure and composition. Nonetheless, both categories offer properties such as functional tunability, structural diversity, and robustness, which are essential for photochemical applications.^{39,40} Owing to these advantages, porous materials have been used for a wide range of photochemical applications, which span from the hydrogen evolution reaction (HER), oxygen evolution reaction (OER), oxygen reduction reaction (ORR), carbon dioxide reduction reaction (CO₂RR), and nitrate reduction reaction (NO₃RR) to various organic transformations (Fig. 1b).^{41–46} A detailed discussion of these categories of porous materials and various applications is beyond the scope of this review. Hence, we will be focusing on the photocatalytic CO₂RR using covalent organic frameworks.

3. Photocatalytic CO₂ reduction mechanism

Photocatalysis involves the conversion of light energy into chemical energy *via* charge separation across the bandgap of the semiconductor to facilitate the redox transformation of chemical moieties on their surface. The photocatalytic transformation on a semiconductor photocatalyst consists of three fundamental steps:

- Visible light absorption: the efficient harnessing of visible rays necessitates that the energy of the irradiated radiation should be greater than the band gap of the photocatalyst (Fig. 2).^{47,48} Therefore, for harnessing solar light, which mainly consists of visible and infrared radiation (95%, UV = 5%), the bandgap should be between 1.7 and 3.1 eV.

- Generation of charge carriers (electron–hole pairs): light absorption leads to the generation of photoexcited e[−]–h⁺ pairs. Notably, the lifetime time of the excited electrons should be sufficient for surface catalytic transformations that typically occur in 10^{−8} to 10^{−1} s compared to charge recombination, which is much faster and requires ~10^{−9} s.⁴⁹ Hence, it is ubiquitous to design materials to maximize light absorption and the lifetime of the excited states. The generated electrons and holes then migrate to the interface of the photocatalyst where the redox reaction takes place, and

- Redox reaction on the photocatalyst surface: alongside the bandgap, the band position of the photocatalyst is pivotal for CO₂ reduction. The LUMO and HOMO of the photocatalyst must straddle the reduction potential of CO₂ and the oxidation potential of the electron donor. In other words, the bottom of the conduction band must be more negative than the reduction potential of CO₂, and the top of the valence band must be at a more positive potential relative to the electron donor including water, triethanolamine (TEOA), and triethylamine (TEA).

Photosensitive units and active sites (oxidation and reduction units) can be incorporated into the COF framework, wherein the COF can act simultaneously as an intrinsic photocatalyst to harness light and perform catalysis. The periodic structure of COFs can provide ample active sites, thereby maximizing performance with

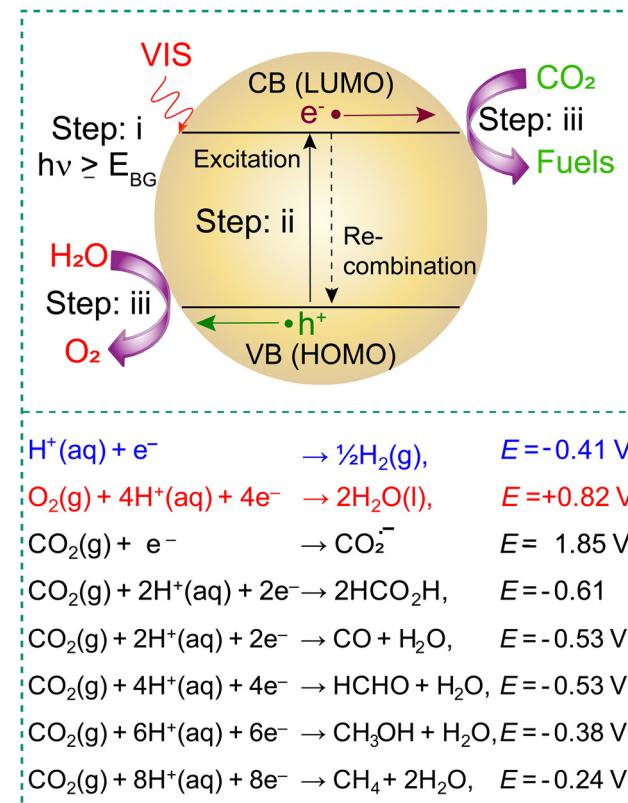


Fig. 2 Mechanism of photocatalytic CO₂ reduction on a semiconductor photocatalyst.

respect to the molecular congeners.⁵⁰ The route followed in such a system is simplistic and the same as described above. However, most COFs have limited light-harnessing capability, necessitating an external photosensitizer typically consisting of Ir and Ru complexes. These complexes are excited upon irradiation, and if the bands are appropriately aligned with the COF, the photogenerated e[−] migrates to the reduction site on the COF, where the CO₂RR takes place. The holes in the photosensitive complex participate in the oxidation reaction. Likewise, if the COF lacks an active centre, chelating ligands can be introduced on the COF backbone to bind with metal atoms (Co, Ni, Fe, Re, *etc.*), acting as the catalytic site. Herein, the COF acts as a photosensitizer, and upon illumination, the electrons from the CB of the COF migrate to the active centre where the CO₂RR takes place while the sacrificial electron donor quenches the holes left. In other cases, the COF backbone can be used as a template to construct heterojunctions with semiconductors like nanoparticles and polyoxometalates that depict a better catalysis than the individual materials. The excited state electron transfer in such hybrid materials is complex and determined through advanced spectroscopic techniques.

4. Challenges of photocatalytic CO₂ reduction

Despite the recent progress in developing CO₂ photoreduction catalysts, several challenges need to be overcome. The challenges



are tuning product selectivity, overcoming the parasitic hydrogen evolution reaction (HER), using metals and sacrificial agents, challenging oxidation half-reaction, overestimating product yield and catalyst decomposition.

4.1. Product selectivity

CO_2 is chemically inert and less reactive due to a high bond energy of 750 kJ mol^{-1} .⁵¹ The reduction of CO_2 is thermodynamically non-spontaneous ($\Delta G > 0$) and is an uphill process. The one-electron reduction of CO_2 has a high reduction potential ($E_{(\text{CO}_2/\text{CO}_2^-)} = -1.85 \text{ V vs. SHE}$) due to the change in geometry from linear to bent, requiring high reorganizational energy, making it challenging to achieve under normal conditions. By contrast, proton-coupled electron transfer (PCET) has much lower reduction potentials that are positive with respect to the conduction band of numerous semiconductors.⁵² Hence, the photoreduction of CO_2 proceeds through the PCET pathway. Here, it is worth noting that the reduction potentials of CO_2 to various products such as CO, HCHO, HCOOH, CH_4 , CH_3OH , and others are close and encompass a narrow range of -0.7 V to -0.2 V at $\text{pH} = 7$.⁵³ This often leads to a mixture of products that are hard to separate owing to their similar properties (Fig. 3a).

The mechanism of formation of these products occurs *via* multi-step PCET and is still ambiguous. However, the first step

is the adsorption of CO_2 through the binding sites in the framework, leading to the subsequent formation of $^*\text{OCHO}$ or $^*\text{COOH}$ intermediates.⁵⁴ Further protonation and desorption lead to the formation of HCOOH , while CO can be formed by reduction. Most COF-based photocatalysts have a weak $^*\text{CO}$ binding energy, usually leading to the formation of CO as the major product. Stronger binding of $^*\text{CO}$ may favor further PCET steps generating $^*\text{CHO}$ and $^*\text{COH}$, ultimately forming CH_3OH and CH_4 . Meanwhile, the two-step H^+/e^- transfer from the $^*\text{OCHO}$ or $^*\text{COOH}$ intermediates promotes formaldehyde generation (HCHO). Notably, photocatalytic conversion of CO_2 to C_2^+ products like $\text{C}_2\text{H}_5\text{OH}$, CH_3CHO , and CH_3COOH is rarely achieved.

4.2. Hydrogen evolution reaction (HER)

Water is an ideal solvent to carry out the CO_2RR as it surpasses the need for undesirable organic solvents, making the overall process much more sustainable. Also, it can simultaneously act as an electron donor to quench the holes and act as a hydrogen source during PCET. The reduction potential of water to hydrogen is $E_{(\text{H}_2\text{O}/\text{H}_2)} = -0.41 \text{ V vs. SHE}$ at $\text{pH} = 7$, and it falls in the range of CO_2 reduction to value-added products.⁵⁵ Moreover, the reduction of CO_2 to CH_3OH , CH_4 , HCHO, *etc.* involves a multielectron transfer, whereas the HER is a two-electron transfer process, making it more feasible. Another concern is

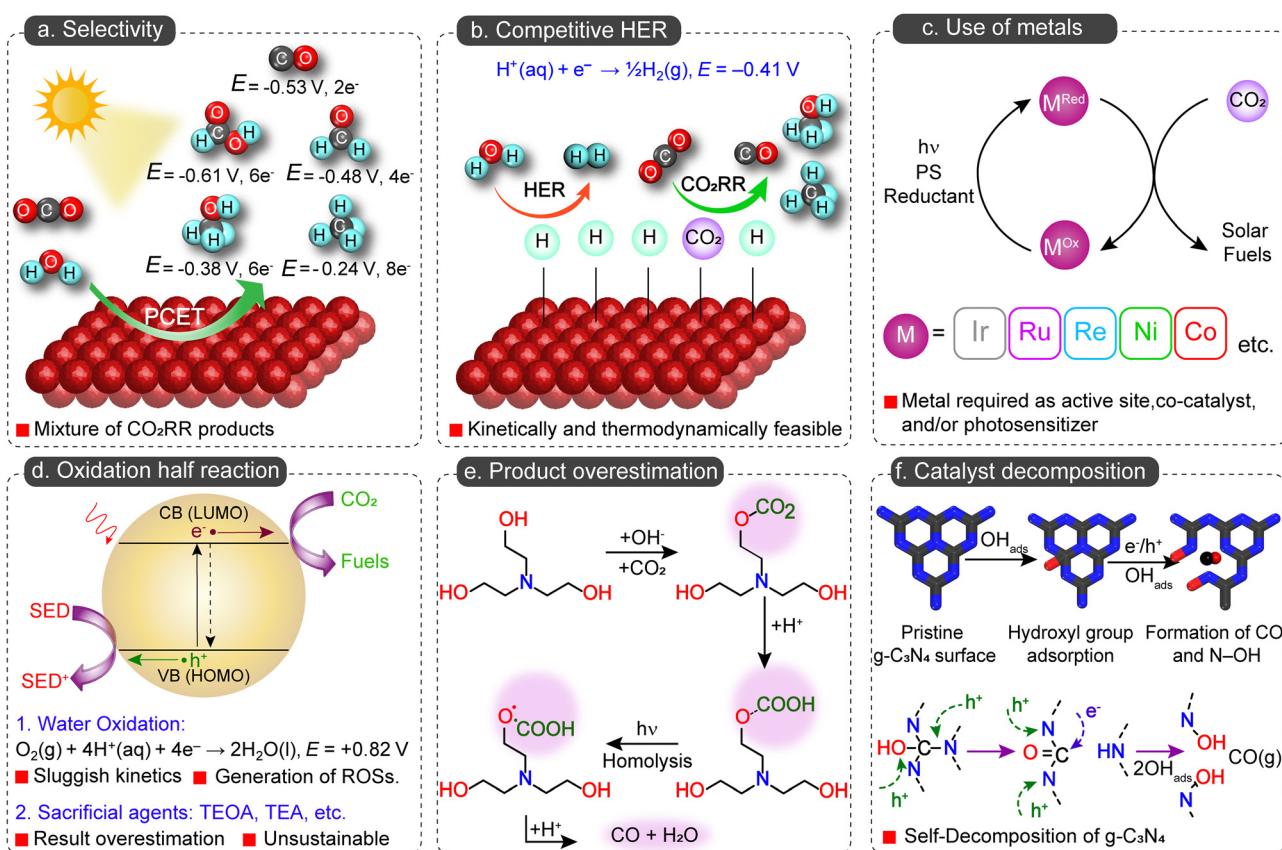


Fig. 3 Challenges of photocatalytic CO_2 reduction. (a) Selectivity of the product formed, (b) competitive hydrogen evolution reaction, (c) use of metals, (d) challenging oxidation half-reaction, (e) overestimation of the product yield, and (f) decomposition of the catalyst under the reaction conditions.

the limited solubility of CO_2 in water, with only 1 molecule of water available for 1300 CO_2 molecules.⁵⁶ Thus, the HER is generally thermodynamically and kinetically feasible compared to the CO_2RR . Hence, the HER is a parasitic reaction to the CO_2RR , particularly for liquid phase reactions (Fig. 3b). This compromises the overall selectivity and efficiency of the process, and attempts need to be made to bypass the HER.

4.3. Use of metals

Significant efforts to design photocatalysts have led to the development of highly efficient CO_2 reduction catalysts. However, many of these photocatalysts rely on transition metals with multiple oxidation states and often require co-catalysts made from expensive metals to enhance their performance (Fig. 3c). Additionally, when COFs exhibit poor light-harvesting capabilities, external photosensitizers containing costly and scarce noble metals like Ru and Ir are frequently employed.⁵⁷ This reliance on expensive materials poses a significant limitation, reducing scalability and making the process unsustainable. Furthermore, transition metal-based catalysts often favor hydrogen evolution reactions (HERs), compromising selectivity. They are also prone to self-oxidation and photo-corrosion and exhibit lower hydrolytic stability. Metal-free systems can be an excellent alternative for their abundance, relatively cheaper cost, environmental friendliness, and sustainability.^{58,59}

4.4. Oxidation half-reaction

The holes generated during the illumination of the photocatalyst can be consumed in the oxidation of water, generating O_2 or hydroxyl radicals (OH^\bullet) as the oxidation half-reaction to the CO_2RR . While the valence band of most semiconductor photocatalysts is more positive than water oxidation ($E_{\text{O}_2/\text{H}_2\text{O}} = 0.81$ vs. NHE at $\text{pH} = 7$), making the oxygen evolution reaction (OER) thermodynamically feasible, being a 4-electron process that makes it challenging. Besides, the accumulation of the evolving oxidizing species OH^\bullet or O_2 on the photocatalyst surface interrupts the CO_2RR . To surpass this challenge, people often use sacrificial agents like alcohol and amines, making the process unsustainable (Fig. 3d).⁶⁰ The catalyst design must be improved to promote water oxidation as a counter-reaction.

4.5. Product overestimation

To improve the solubility of CO_2 , the dispersibility of the heterogeneous photocatalysts, and recyclability, alternative organic solvents like acetonitrile (ACN), ethyl acetate (EAA), and dimethylformamide (DMF) are often used instead of water. Solvents may exhibit photoactivity and undergo decomposition under certain conditions, such as specific light wavelengths, solvent combinations, temperature, and pressure (Fig. 3e). This can lead to generating one of the CO_2 reduction products, causing inaccurate assessment of the catalyst's efficiency and making the overall process ambiguous.⁶¹

As discussed, sacrificial agents like triethanol amine (TEOA) and triethyl amine (TEA) are used as sacrificial electron donors. It has also been reported that they can catalyze CO_2 photo-reduction to CO and CH_4 through hydrogen atom transfer

(HAT). *In situ* FTIR studies and density functional theory (DFT) calculations strongly support the idea that the terminal $-\text{OH}$ group in TEOA can behave as the active centre.^{62,63} Unfortunately, possible solvent decomposition and sacrificial agent participation are often unnoticed when considering solvent and electron donor selection as a parameter for enhancing efficiency.

4.6. Catalyst decomposition

It has been confirmed that graphitic carbon nitride ($\text{g-C}_3\text{N}_4$) undergoes self-decomposition in light to generate CO , CO_2 , NO_2 , and $\text{NO}_2^-/\text{NO}_3^-$ under the reaction conditions (Fig. 3f).⁶⁴ The rate of CO production in the argon atmosphere was almost equal to that in the CO_2 atmosphere. The mechanistic studies revealed that the instability was due to the electronic interaction between the adsorbed hydroxyl group and $\text{g-C}_3\text{N}_4$, which reduces the stability of the $\text{C}=\text{N}=\text{C}$ bonds. Unfortunately, there are limited studies on the behavior of COF-based photocatalysts, and they need to be looked into in-depth, as the organic components in COFs are prone to photodegradation.

5. Favorable properties of porous materials as photocatalysts

Compared to the traditional non-porous congeners, where only surface sites are accessible for photocatalysis, the porous photocatalyst offers certain advantages. We will be discussing it in this section.

5.1. Structural tailorability

COFs are designed through the principle of reticular chemistry, enabling atomically precise control of the chemical and topological structure that sets them apart from other classes of semiconductor photocatalysts like metallic oxides and porous polymers (Fig. 4a).^{65,66} The predetermined connections enable the design of a framework with a high surface area, desired pore environment, and hierarchical structures. Also, for similar topology, the pore sizes can be controlled simply by varying the length of the building blocks. The geometry of the linkers can be varied to fabricate three-dimensional structures, enhancing the accessibility of the active sites.

5.2. Active site engineering

The precursors can be designed to integrate the catalytically active moieties in the framework, which improves photocatalytic efficiency by decreasing the overall inactive components.^{67,68} The building blocks are chosen to enhance the light-harnessing capability, tune the band gap, maximize CO_2 absorption, and promote mass transfer (Fig. 4b). The functional components with high π -conjugation can be incorporated to manipulate the bandgap and promote charge separation and transfer. Alternatively, COFs with poor photosensitivity or lacking active sites can also be modified by post-synthetic modification to incorporate active components or by using the nanoconfinement effect of COFs.

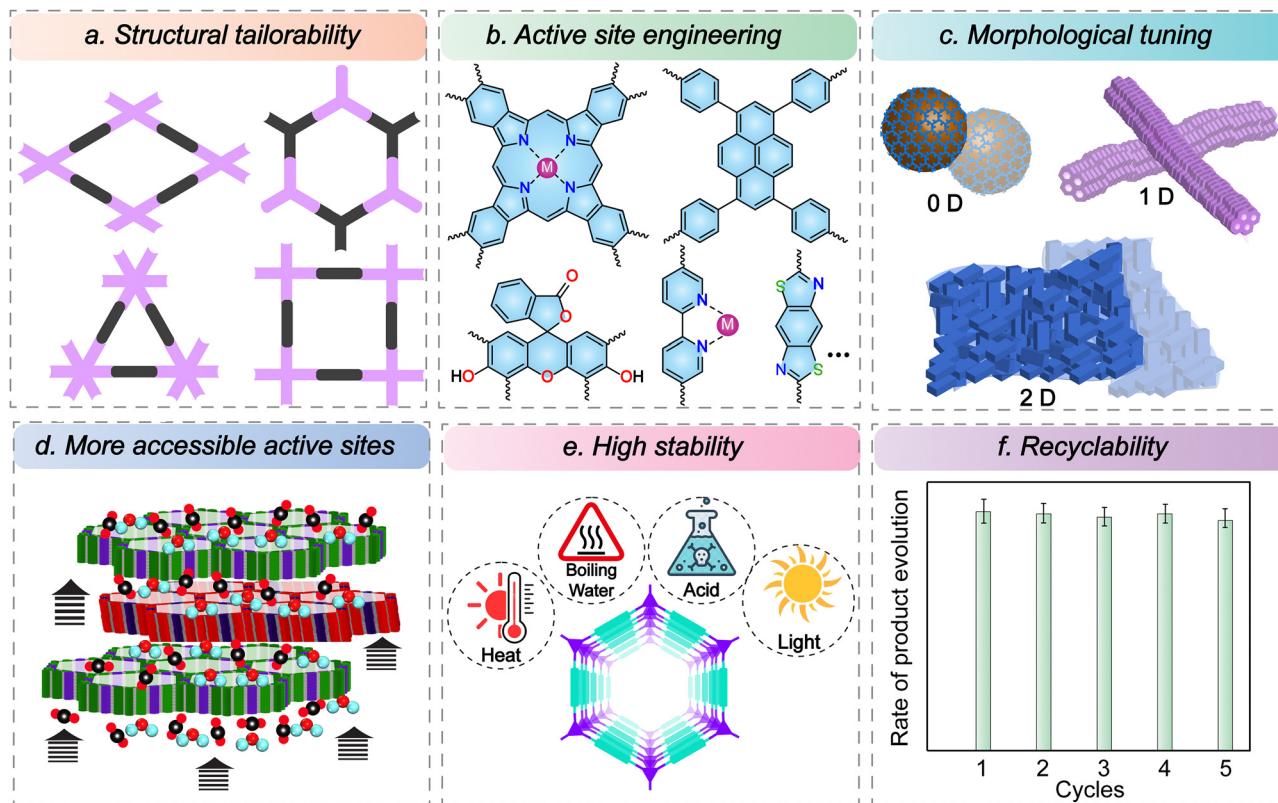


Fig. 4 Favorable properties of porous materials as photocatalysts.

Broadly, these linkers can be classified into metalated and metal-free analogues. The building units can be engineered to anchor various photoactive metals as single atom sites, which helps greatly enhance performance by using a lesser quantity of metals than the bulk metallic catalyst. The strategy has allowed the incorporation of photoactive units to anchor the metal atoms, such as porphyrin, phthalocyanine, bipyridine, salen, and diol. Another pathway is incorporating building units that are highly conjugated, which acts as a photo absorber, thereby precluding the requirement of expensive photosensitizers. These include units like pyrene, eosin, perylene, and thiafulvalene. These moieties are excellent light absorbers and efficiently generate charge separation. Also, the principle of reticular chemistry can be used to engineer electron-rich donor and electron-poor acceptor sites that promote HOMO-LUMO separation and intramolecular charge transfer *via* the push-pull effects. Furthermore, incorporating heteroatoms helps in the adsorption and conversion of CO_2 .

5.3. Morphological tuning

The morphological effect is one critical yet often overlooked parameter in tuning the catalytic performance. Dimensionality can have a profound impact on the catalytic performance. The reticular synthesis enables complete structural control of the porous materials. Beyond that, supramolecular nanosynthesis allows for some degree of morphological tuning. Different morphologies can be obtained with the same set of linkers

and common topology. The most common are 0D spheres, 1D fibres/tubes/rods, and 2D sheets (Fig. 4c).^{69–71} The morphology greatly influences the final processability and properties of the material.⁷² For example, the spheres can have colloidal stability and dispersibility for otherwise insoluble COFs. Likewise, fibres and tubes have high aspect ratios, enhancing the active surface areas. The synthetic methodology enables control of the size of the 0D spheres as well as particle size uniformity. Recent works have also led to the development of COFs with monolayers, a few layers to films of several micrometre thickness. Besides, they can also be grown on different substrates depending upon the application. The two-dimensional materials can also be exfoliated to synthesize nanosheets with much higher mass transport and ease of accessing active sites. Because of a higher degree of morphological control, these materials can be synthesized as powders, films, and foams, based on the application requirement. However, there is a lack of comprehensive studies exploring the impact of morphology and dimensionality on catalytic performance and light penetration, highlighting the need for further investigation.

5.4. More accessible active sites

The unique design of COFs bestows them with periodic and well-defined pore channels. This promotes the mass transfer and diffusion of the substrates and products throughout the bulk, and the catalysis is not restricted to the surface-exposed active sites. The porous frameworks facilitate the confinement



of suitable substrates, bringing them in proximity and promoting reaction rates compared to the non-porous congeners. The accessibility to the active sites can be further increased by fabricating ultrathin covalent organic nanosheets (CONs) with only a few layers of thickness (Fig. 4d).⁷³ This can be achieved by either a top-down approach where a 2D COF is exfoliated or a bottom-up approach where structuring tuning and reaction methodology enable the growth of one or a few layers of CONs. In either case, the synthesized CONs have an even higher active surface area and shorter diffusion lengths than the bulk counterparts, leading to enhanced catalytic performance. Another vital strategy to augment active site accessibility is changing the material dimensionality from 2D to 3D. Although the synthesis of 3D COFs is comparatively more challenging, they can accomplish much higher surface areas and pore sizes, leading to an improvement in CO₂ mass transfer and making the active sites more accessible.^{74,75}

5.5. High stability

Despite achieving high catalytic performances using transition metal complexes and other metallic systems, one of the significant drawbacks is their poor hydrolytic and photostability. In this context, COFs linked through robust covalent bonds are much more stable (Fig. 4e). Traditionally, COFs were synthesized using reversible reactions such as boronate ester condensation and imine linkages. While these methods produced highly crystalline structures, they often exhibited poor stability, especially in water and under light irradiation.⁷⁶ However, several methodologies, like post-synthetic modifications and interlayer hydrogen bonding, have been devised to improve their stability. Alternatively, β -ketoenamine COFs synthesized by the combination of reversible and irreversible pathways allowed the construction of COFs that were simultaneously crystalline and stable.⁷⁷ However, long-range conjugation is impeded in such systems, compromising their charge transfer and, eventually, catalytic performances in some cases. In this context, the $-\text{C}=\text{C}-$ linked COFs that are exceptionally chemically stable and have extended π -conjugated systems come to the rescue.^{78,79} Nonetheless, the crystallization of COFs based on irreversible reactions remains challenging. Hence, decades of research on COFs enables the choice from a wide range of linkages like imidazole, olefin, keto-enamine, and benzoxazole, which are highly promising as robust platforms for CO₂ photoreduction.⁸⁰⁻⁸³ It is worth mentioning that there are limited studies on the degradation mechanisms of these COFs under photoirradiation, and it largely remains unclear.

5.6. Recyclability

One crucial parameter that sets apart homogeneous catalysts from their heterogeneous analogues is recyclability. Porous materials like COFs are generally insoluble in most organic solvents. They can be easily recovered from the reaction medium by centrifugation or filtration.⁸⁴ Hence, they can be used for several cycles, making the overall process cost-effective and sustainable (Fig. 4f). The post-synthetic structural and morphological studies have shown that COFs can maintain their

catalytic performance and selectivity over several cycles while maintaining structural integrity.

The ability to independently adjust these factors strengthens the potential of reticular chemistry in shaping the development of advanced next-generation CO₂ reduction catalysts.

6. COFs as heterogeneous platforms for photocatalytic CO₂ reduction

The covalently linked frameworks of covalent organic frameworks (COFs) impart exceptional structural robustness and extended π -conjugation, enhancing charge transport and stability under reaction conditions. Additionally, COFs facilitate the anchoring of single-atomic metallic sites *via* specific binding sites on their backbone, significantly reducing noble metal usage and promoting sustainability. The ability to engineer COFs in diverse morphologies supports their integration into advanced device architectures, paving the way for next-generation photocatalytic systems.

Based on the properties of COFs, they can behave as photosensitizers and/or active catalysts. Generally, COFs have poor catalytic efficiency; hence, the COF structure is tailored to incorporate active metal sites for CO₂ photoreduction. Based on this, COF-based photocatalysts can be divided into two subclasses: (i) metalated and (ii) metal-free. Among the metalated COF catalysts, there are three essential classes: (1) COFs with predetermined inherited active sites: inspiration can be taken from well-studied homogeneous molecular catalysts wherein the building blocks of the COFs can be judiciously designed to incorporate the active sites (Fig. 5a). Due to cooperative effects, multiple active sites within a single framework in proximity can give rise to a better performance than the homogeneous counterparts. Moreover, they are easier to recover and reuse, making them appealing for large-scale applications. These features create a foundation for designing highly active photocatalysts and investigating atomic-level structure–property relationships. The tuning of the metal centres and their oxidation state can vary the selectivity and efficiency of the process. (2) Post-synthetic modification to introduce single-atomic metal sites: porous materials can be used as a porous support for anchoring single-atom active sites (Fig. 5b). Along with grafting metal centres within the building blocks used to synthesize photoactive COFs, another important strategy is the post-synthetic incorporation of precise active sites using various coordinating sites in the framework. The local environment of the metal atoms can be easily tuned by meticulous choice of linkers based on heteroatom donors like N, O, and S. Besides, the same linkers can be used to incorporate various metallic sites. Dual metal coordination is another critical approach wherein two atomically dispersed metal sites work in synergy. In this regard, Ni–Co, La–Ni, and Cu–Ni sites have been incorporated to tune the performance and improvise over single metal coordination. This strategy opens new avenues for single-atom catalysis using porous materials. (3) COFs as porous organic supports for



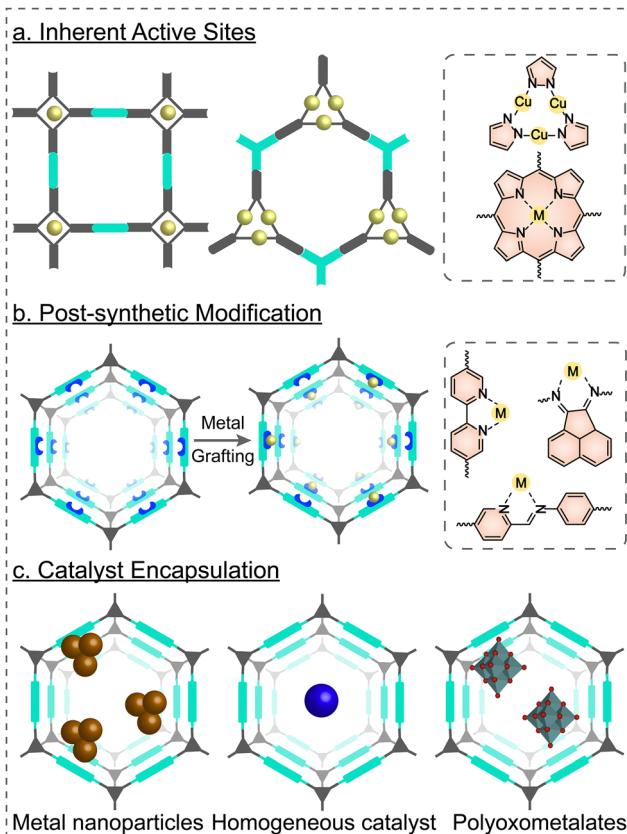


Fig. 5 Various strategies for fabricating metalated covalent organic frameworks for photocatalytic CO_2 reduction.

encapsulation of homogeneous catalysts: COFs can act as excellent scaffolds for encapsulating active catalysts within their pores to form heterostructures for photocatalytic CO_2 reduction (Fig. 5c). COFs can provide a hydrophobic micro-environment and promote catalysis in the aqueous environment, even for catalysts with poor hydrolytic stability, while the porous nature will simultaneously promote the rapid diffusion of substrates and products. Moreover, the COF pore enables the proximity of catalysts and substrates, enhancing the reaction rate. The catalyst can be immobilized by both covalent and non-covalent interactions. Significant progress has been made in this regard, and various catalysts, such as MOFs, polyoxometalates, metal/metal oxide nanoparticles, quantum dots, and carbon nanodots, have been encapsulated within the COF backbone.

Another important category of COFs for CO_2 photoreduction is the metal-free analogues. These COFs usually act as both photoabsorbers and active catalysts. The optoelectronic properties can be tuned by selecting the building blocks from a large pool of π -conjugated and aromatic systems to enable efficient charge separation and migration. Moreover, heteroatom sites can be incorporated into the framework to enhance CO_2 uptake through CO_2 polarisation through the dipole–quadrupole interactions. We will be discussing these strategies in detail in the subsequent sections.

6.1. Metalated COFs as single-atom heterogeneous catalysts for photocatalytic CO_2 reduction

The large surface areas, well-defined pore channels, and abundant periodic linkers make COFs excellent porous scaffolds for introducing metallic sites for developing single-atom heterogeneous catalysts for photocatalytic CO_2 reduction. The excellent photo-absorbing capability of COFs can be coupled with the inherent catalytic efficiency of the metal centres. Reticular chemistry enables designing COFs with inherent metallic sites or the post-synthetic introduction using chelating ligands meticulously engineered on the COF backbone. The metal atoms control the selectivity and efficiency of the photocatalytic CO_2 reduction by the variation in the binding affinities of CO_2 and the subsequent intermediates generated during CO_2 transformation. This can be tuned by varying the metal centres and their coordination environments. Over the years, several ligands have been designed to incorporate active metal sites in the COF framework, like bipyridine, catechol, porphyrin, salen, and acenaphthylene-1,2-diimine. They play a pivotal role in modulating the coordination environment of metal centers in COFs. The different combinations of chelating groups like N_4 , N_3O , N_2O_2 , N_3O , and O_4 can influence the strength and performance of the co-ordinated active metal sites. For instance, chelating ligands that create a more rigid coordination environment may stabilize the metal centre and improve its longevity during photocatalytic cycles, while the presence of specific functional groups on the ligand may tune the redox potential of the metal, affecting the photocatalytic performance. Ligands like porphyrin have inherent light harnessing capability and the robust N-macrocyclic core provides an ideal platform for co-ordinating a wide range of metal sites like Cu, Co, Ni, Fe, and Zn among others both pre- and post-synthetically.

6.1.1. Bipyridine (bpy) based COFs. 2,2'-Bipyridine (bpy) is an appealing scaffold widely explored for immobilizing metal atoms owing to their planar structure, ease of coordination, and strong chelating ability. A vacant π^* orbital enables the metal to ligand charge transfer (MLCT) with various metals, imparting intriguing photophysical properties.⁸⁵ In a seminal work conducted by Huang and co-workers, a Schiff base COF was fabricated through the solvothermal reaction by the condensation of C_2 aldehyde BPDA (2,2'-bipyridyl-5,5'-dicarboxaldehyde) with C_3 amine TTA (4,4',4''-(1,3,5-triazine-2,4,6-triyl)trianiline) (Fig. 6a).⁸⁶ Subsequently, Re active sites were post-synthetically incorporated by stirring with $\text{Re}(\text{CO})_5\text{Cl}$ to form the Re-COF. The transient absorption (TA) spectroscopy studies showed a longer lifetime of the Re-COF in comparison to the pristine COF, which results from electron transfer (ET) from COFs to $\text{Re}(\text{bpy})(\text{CO})_3\text{Cl}$ as observed from X-ray transient absorption (XTA) spectroscopy. Accordingly, the photocatalytic CO_2 RR performance of the Re-COF was monitored by dispersing the catalyst in acetonitrile and using TEOA as a sacrificial donor. Interestingly, the Re-COF generated CO at the rate of 15 mmol g^{-1} for over 20 hours with a TON of 48 and selectivity of $\sim 98\%$, demonstrating 22 times better performance than the homogeneous analogue. Notably, *in situ* diffuse reflectance



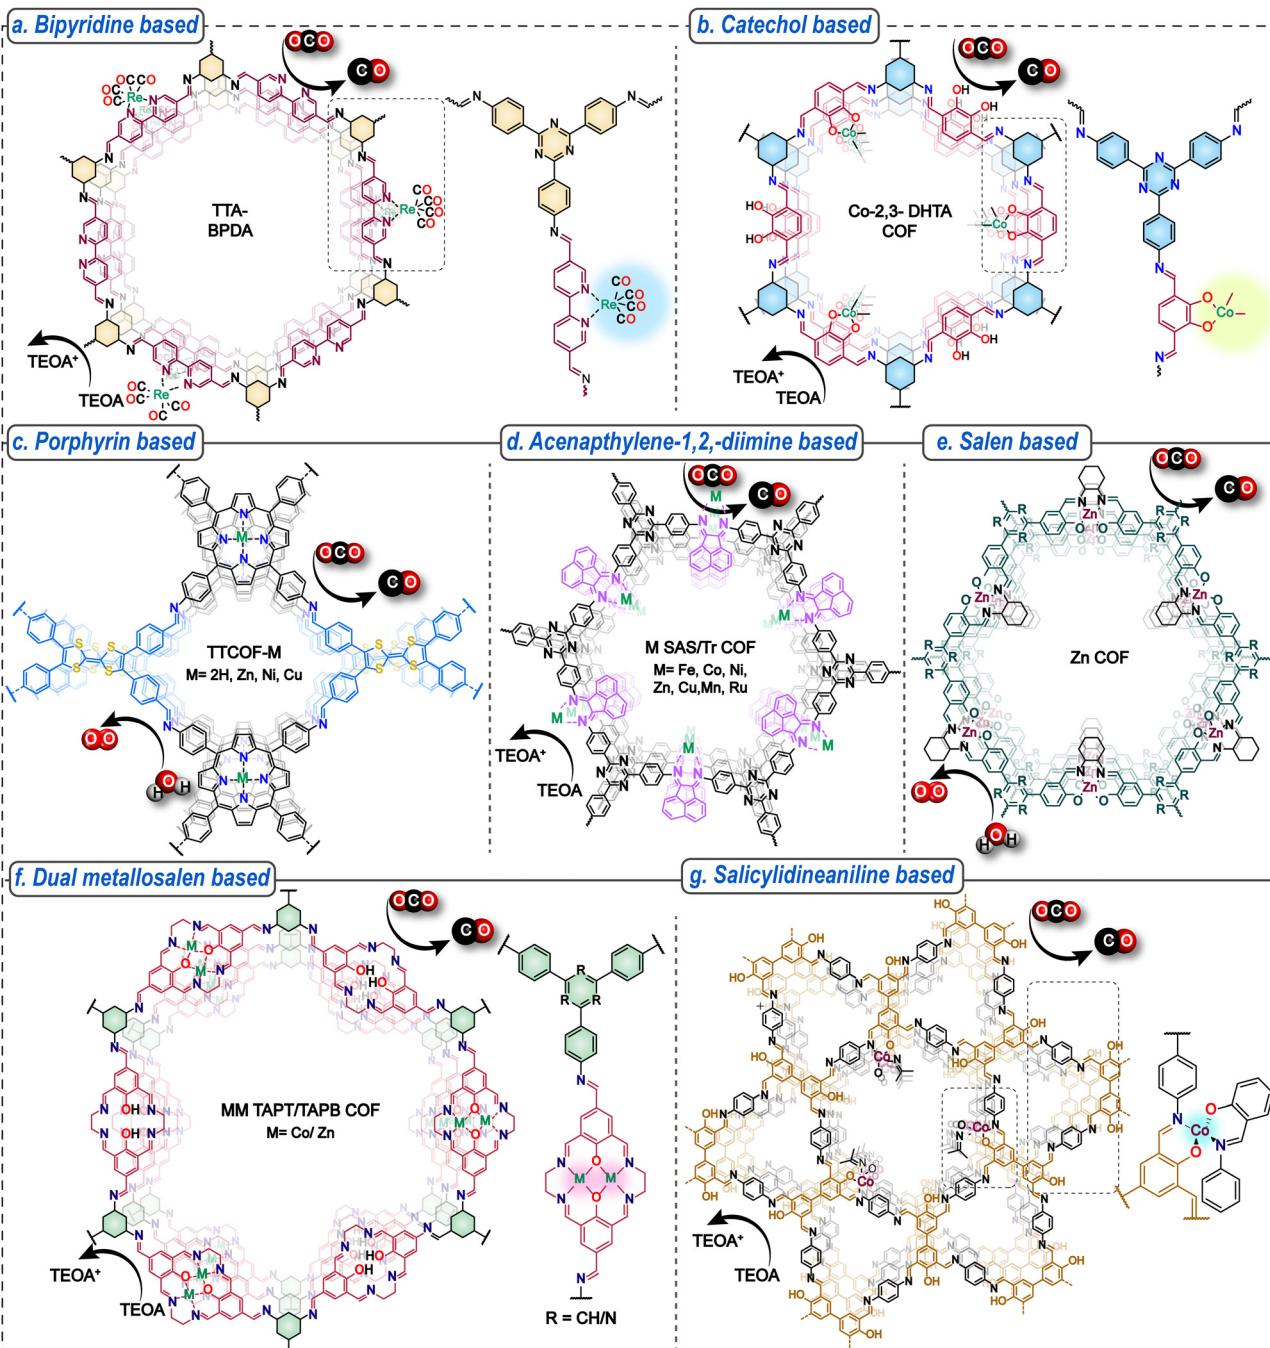


Fig. 6 COF-based single-atom catalysts for photocatalytic CO_2 reduction. The chemical structures of the COFs representing the ligand system and active metals involved.

UV-visible spectra under the reaction conditions were used to gain mechanistic insights, thereby providing fascinating insights into the CO_2 reduction process.

The concept was further extended by designing a $-\text{C}=\text{C}-$ bonded Re-Bpy- sp^2c -COF synthesized by the condensation of $4,4',4'',4'''$ -(pyrene-1,3,6,8-tetrayl)tetrabenzaldehyde (TFPPy) and $5,5'$ -bis(cyanomethyl)-2,2'-bipyridine and loading with $[\text{Re}(\text{CO})_5\text{Cl}]$.⁸⁷ Compared to imine COF congeners, the sp^2c -COF has broader light absorption due to extended conjugation and

higher structural robustness due to stronger bonds. Under the optimized conditions, the Re-Bpy- sp^2c -COF converted CO_2 to CO at $1040 \mu\text{mol g}^{-1} \text{h}^{-1}$ with 81% selectivity and a TON of 18.7. The material maintains its crystallinity and catalytic performance effectively for up to 17.5 hours of photocatalysis. However, after prolonged irradiation beyond 50 hours, a notable reduction in crystallinity and catalytic efficiency is observed. The homogeneous molecular catalyst $[\text{Re}(\text{bpy})(\text{CO})_3\text{Cl}]$ showed a much lower TON of 10.3 and was deactivated after three hours. Interestingly, the CO

production rates can be further enhanced to $1400 \mu\text{mol h}^{-1} \text{g}^{-1}$ with 86% selectivity for over 5 h by using photoactive dyes in conjunction with the Re-Bpy-sp²c-COF. Notably, loading the Re-Bpy-sp²c-COF with varying amounts of Pt co-catalyst can generate tunable syngas with the CO:H₂ ratio ranging from 4:1 to 1:10. Another -C=C- bonded COF viCOF-bpy-Re was formed through condensing trimethyltriazine and 2,2'-bipyridyl-5,5'-dialdehyde. The rational incorporation of Re as the reduction site and triazine core as the oxidation site promoted efficient charge separation, leading to simultaneous CO₂ reduction to CO with a $190.6 \mu\text{mol g}^{-1} \text{h}^{-1}$ rate and 100% selectivity and water oxidation to O₂.⁸⁸ The robust sp² linkage led to excellent catalytic stability for over 50 h.

Furthermore, a β -keto-enamine-linked TpBpy COF was explored for photocatalytic CO₂ reduction by decorating it with Ni active sites.⁸⁹ The photocatalytic performance was evaluated in an aqueous medium using [Ru(bpy)₃]Cl₂ as the photosensitizer and TEOA as the sacrificial agent. Ni-TpBpy generated $4057 \mu\text{mol g}^{-1}$ CO in 5 h with 96% selectivity compared to pristine TpBpy, which produces only $4 \mu\text{mol h}^{-1}$ CO with 83% selectivity. Interestingly, an imine-bonded Ni bipyridine COF shows a much inferior performance at $0.7 \mu\text{mol}$ of CO and $S_{\text{CO}/\text{H}_2} = 58\%$, highlighting the importance of keto formation in stabilizing the key intermediates by H-bonding interactions during catalysis. The work provides important insights into tuning the structure to improve selectivity over the competing hydrogen evolution reaction.

Thus, the bipyridine core stands out for its facile synthesis and the ease of integration into different COF systems, connected *via* various linkages such as imine, vinylene, and β -keto-enamine. This variation in linkages can influence the conjugation length, which in turn affects the optoelectronic properties and long-term recyclability of the materials. The adjacent N atoms in 2,2'-bipyridine are susceptible to functionalization with most transition metals including Re, Ni, Co, Cu, Ru, Ir, etc., making them excellent candidates for a range of photocatalytic reactions.

6.1.2. Catechol-based COFs. The coordination environment of the metal species within the COF plays a pivotal role in determining the photocatalytic CO₂ reduction performance. Keeping this in perspective, the M-O₄ microenvironment was designed by incorporating aromatic catechol moieties in the COF backbone by the Schiff base condensation of 2,3-dihydroxybenzene-1,4-dicarboxaldehyde (DHTA) aldehyde containing predesigned -OH moieties with 2,4,6-tris(4-aminophenyl)-1,3,5-triazine (TAPT) amine (Fig. 6b). The catechol moieties strongly coordinate with Co(II) and generate a distinct Co-O₄ site by coordinating with two other water molecules. The Co-COF demonstrates a CO production rate of $18\,000 \mu\text{mol g}^{-1} \text{h}^{-1}$, $S_{\text{CO}/\text{H}_2} = 95.7\%$, and a TOF of 111.8 h^{-1} in 4:1 MeCN/water solution using [Ru(bpy)₃]Cl₂ as a photosensitizer and TEOA as an ED under visible light irradiation.⁹⁰ Notably, the CO production rate of Co-2,3-DHTA-COF was 23.6 times that of the pristine 2,3-DHTA-COF. Interestingly, another keto-enamine linked Co-TP-TAPT COF having a coordination mode of Co-O₃N showed much lower $R_{\text{CO}} = 11\,600 \mu\text{mol g}^{-1} \text{h}^{-1}$ and $S_{\text{CO}/\text{H}_2} = 76.6\%$. The results

highlight the role of the microenvironment in determining the CO₂ reduction efficiency and selectivity, with the Co-O₄ coordination mode being more active than the Co-O₃N site.

6.1.3. Porphyrin-based COFs. Porphyrin-based homogeneous catalysts are among the most well-studied for their photocatalytic CO₂ reduction performance. Their excellent catalytic performance is attributed to their strong chelating ability to various metal ions, inherent photosensitizing capabilities, and modular electronic and photophysical properties.⁹¹ A series of imine-linked COFs were synthesized by meticulously integrating electron-deficient metalloporphyrin, having superior light-harnessing ability and electron-rich tetrathiafulvalene known for their electron donation ability and fast charge transfer. The TTCOF-M (M = 2H, Zn, Ni, Cu) was made *via* imine condensation reaction of metalated C₄ amine 5,10,15,20-tetrakis(4-aminophenyl)porphyrin-M and C₄ aldehyde 4,4',4'',4'''-[[2,2'-bi(1,3-dithiolylidene)]-4,4',5,5'-tetracyl]tetrabenzaldehyde (TTF-4CHO) (Fig. 6c).⁹² The design enabled simultaneous CO₂ reduction and water oxidation. The photocatalytic CO₂ reduction performance was monitored by dispersing the COF photocatalyst in water without using any external photosensitizer, SED, or co-catalysts. TTCOF-Zn demonstrated the best CO evolution of $12.33 \mu\text{mol}$ in 60 h with 100% selectivity, followed by TTCOF-Cu (8.65 μmol) and TTCOF-Ni (0.462 μmol). The work emphasizes the importance of optimizing band positions to enhance the challenging water oxidation reaction as the counterreaction, while simultaneously overcoming the competing hydrogen evolution reaction (HER) to achieve high selectivity.

In another report, a series of Co-porphyrin donor-acceptor COFs were synthesized by varying the charge-carrier density and π -conjugation length of the donor group to gain essential insights into the role of electronic structure in CO₂ reduction performance. Three COFs were synthesized by the Schiff base condensation of Co-5,10,15,20-tetrakis-(4-aminophenyl)-porphyrin acceptor and donor moieties based on benzodithiophene (BDT), thienothiophene (TT), or phenyl (TA).⁹³ Subsequently, the photocatalytic CO₂ reduction performance was monitored by dispersing the COF photocatalyst in MeCN and using Re-(bpy)(CO)₃Cl as a photosensitizer and TEOA as a SED. Clearly, a BDT bearing COF showed the best CO evolution rate of $1424 \mu\text{mol g}^{-1} \text{h}^{-1}$. The other COFs bearing thienothiophene or phenyl groups demonstrated much inferior performance of R_{CO} (Co-Por-TT) = $1182 \mu\text{mol g}^{-1} \text{h}^{-1}$ and R_{CO} (Co-Por-TT) = $642 \mu\text{mol g}^{-1} \text{h}^{-1}$. The results highlight that longer conjugation lengths and better donation ability are associated with higher charge carrier mobility and reduced exciton binding energy, leading to better performance.

Recently, a robust imidazole-linked photoactive M-Por-Py-COF (M = Co²⁺, Ni²⁺, Cu²⁺, and Zn²⁺) was demonstrated for photocatalytic CO₂ conversion.⁹⁴ Besides structural robustness, the imidazole group also shows a high affinity towards CO₂ uptake. The photocatalytic CO₂ reduction by dispersing the catalyst in a MeCN/water mixture, using Ru(bpy)₃Cl₂·6H₂O as the photosensitizer and TEOA as the SED showed that the Co-Por-Py-COF gave the best CO production rate of $9645 \mu\text{mol g}^{-1} \text{h}^{-1}$



with 96.7% selectivity, more than 45 times higher than the pristine COF. Interestingly, the Ni-Por-Py-COF further tandem catalyzes the subsequent reduction of the generated CO to CH_4 at the rate of $463.2 \mu\text{mol g}^{-1} \text{h}^{-1}$. The metal centres act as active sites for CO_2 photoreduction by promoting CO_2 adsorption and stabilizing the reaction intermediates and the final desorption of the produced CO.

6.1.4. Acenaphthylene-1,2-diimine-based COFs. In an interesting approach, Hou *et al.* demonstrated the generation of M-N-Cl coordinating centres directly within the COF linkages formed during the synthesis, rather than relying on pre-designed coordinating groups in the building blocks as seen in previous strategies. The Tr-COF was synthesized by the condensation of heteroatom-rich 4,4'4''-(1,3,5-triazine-2,4,6-triyl)-trianiline and ace-naphthenequinone precursors, which were post synthetically impregnated by various metal atoms (Fe, Co, Ni, Zn, Cu, Mn, and Ru) to generate the crystalline M SAS/TrCOF (Fig. 6d).⁹⁵ Subsequently, the photocatalytic CO_2 reduction performance of the catalyst was measured by dispersing it in an acetonitrile/water mixture using TEOA as the SED and $[\text{Ru}(\text{bpy})_3]\text{Cl}_2$ as the photosensitizer. Among all the metalated COFs, the Fe SAS/TrCOF gave the best performance, followed by Co, Ni, Cu, Mn, Zn, and Ru. Optimization of the metal loading of iron demonstrated that 1.1 wt% Fe SAS/Tr-COFs showed the best photocatalytic CO_2 reduction performance with a CO evolution rate of $980.3 \mu\text{mol g}^{-1} \text{h}^{-1}$ with 96.4% selectivity over the parasitic HER, TON of 4.9, and AQY of 3.17% at 420 nm. By contrast, 0.6 wt% and 4.8 wt% Fe SAS/Tr-COFs demonstrated much lower CO evolution of $1799.4 \mu\text{mol g}^{-1}$ and $682.8 \mu\text{mol g}^{-1}$, respectively, after 4 h of reaction. The CO evolution rate was 26 times higher than the pristine Tr-COF, with a selectivity of 62.1% and an AQY of 0.54% at 420 nm. The better CO_2 conversion efficiency of the Fe SAS/TrCOFs could be the result of the synergistic effect of the single atomic metal centres and the COF host that is responsible for the promotion of CO_2 uptake, reducing the energy barrier for forming the $^*\text{COOH}$ intermediate and the subsequent $^*\text{CO}$ desorption as depicted by the DFT studies.

The above study suggests that acenaphthylene-1,2-diimine presents a promising platform for CO_2 photoreduction as it can bypass the use of predesigned metal co-ordinating ligands in the building blocks. Hence, more studies are required in this direction to unlock its full potential.

6.1.5. Metallo-salen-based COFs. The Schiff base condensation of aldehyde bearing *ortho* hydroxy groups with an amine leads to the generation of salen linkage having N_2O_2 pockets capable of strongly binding transition metal ions generating a stable chelate complex. A salen-decorated COF was designed as a three-in-one system for photocatalytic CO_2 reduction in diluted CO_2 (15%) by combining CO_2 enrichment, reduction, and water oxidation in a single material. The Zn-S-COF was synthesized by the imine condensation of (1*R*,2*R*)-(-)-1,2-cyclohexanediamine with *o*-hydroxy bearing trialdehyde 1,3,5-triazine-2,4,6-tris(4'-hydroxy-5'-formylphenyl)benzene (THFB) in the presence of zinc perchlorate hexahydrate (Fig. 6e).⁹⁶ The as-synthesized COF was subsequently loaded with 1-ethyl-3-methylimidazole tetrafluoroborate ($[\text{Emim}]\text{BF}_4$) porous liquid

known for its CO_2 uptake capability, enhancing the local concentration of CO_2 even under the diluted reaction conditions, to synthesize the $[\text{Emim}]\text{BF}_4@\text{Zn-S-COF}$. The optimized CO evolution rate for the $[\text{Emim}]\text{BF}_4@\text{Zn-S-COF}$ was $267.9 \mu\text{mol g}^{-1} \text{h}^{-1}$, 17 times higher than the parent Zn-S-COF, with 97.6% selectivity and an AQE of 2.8% at 420 nm, highlighting the importance of the loaded porous liquid. At low concentration of CO_2 , the CO production rate was $105.9 \mu\text{mol g}^{-1} \text{h}^{-1}$ with ~95% selectivity, while a negligible amount of CO was produced from the Zn-S-COF without the porous liquid. The results underscore the importance of CO_2 enrichment by the porous liquid under dilute conditions in determining the reduction efficiency. Interestingly, replacing the triazine core in the monomer with a benzene core to synthesize the $[\text{Emim}]\text{BF}_4(56.41 \text{ wt}%)@\text{Zn-CCOF}$ gave much inferior performance with $R_{\text{CO}} = 128.6 \mu\text{mol g}^{-1} \text{h}^{-1}$, more than two times lower than the $[\text{Emim}]\text{BF}_4@\text{Zn-S-COF}$. Furthermore, varying the metal centres showed that the Zn-S-COF performed better than Co or Ni-loaded materials under identical conditions.

In another fascinating report, mononuclear ($\text{M-N}_2\text{O}_2$) and binuclear salen ($\text{M-N}_2\text{O}_2-\text{M-N}_2\text{O}_2$) metal sites, where $\text{M} = \text{Zn/Co}$, were incorporated in COFs for tunable syngas production by controlling the metal centres and their coordination environments. The crystalline M(salen)-COF-1 was obtained by the one-step Schiff base reaction of 1,4-hydroxyisophthalaldehyde (or 2-hydroxybenzene-1,3,5-tricarbaldehyde), ethylenediamine, metal acetate, and C_3 amine (1,3,5-tris(4-aminophenyl)benzene (TAPB)/2,4,6-tris(4-aminophenyl)-1,3,5-triazine (TAPT)) (Fig. 6f).⁹⁷ Likewise, M(salen)-COF-2 was synthesized by the two-step reaction involving the synthesis of MM-CHO/M-CHO followed by the Schiff base reaction with TAPT or TAPB amine. Subsequently, the photocatalytic CO_2 reduction performance of Zn-TAPB-COFs, ZnZn-TAPB-COFs, Co-TAPB-COFs, and Co-TAPT-COFs was evaluated to determine the role of the synthetic protocol, coordination mode, metallic site, and ligand. COFs with Zn metal sites (Zn-TAPB and ZnZn-TAPB COFs) demonstrated lower CO and higher H_2 production rates. In contrast, COFs bearing Co centres (Co-TAPB and Co-TAPT COFs) generated much higher amounts of both CO and H_2 . Notably, Co-TAPT-COF-1 showed a much higher photocatalytic activity than Co-TAPT-COF-2, bearing a similar chemical structure, highlighting the role of the synthetic protocol in the reaction efficiency. The superior performance of Co-TAPT-COF-1 can be attributed to its higher crystallinity and the nanotubular superstructure. Moreover, Co-TAPT-COF-1 demonstrated higher syngas production rates than Co-TAPB-COF-1, suggesting the importance of ligands in tuning the catalytic performance. Interestingly, tuning these parameters can control the H_2/CO ratios in the resulting syngas from 1:1 to 30:1.

Although metallo-salen-based COFs are versatile in terms of metal binding, one significant drawback is the limited stability of the salen linkage. Thus, large scale applications of these materials require improvement in their structural stability.

6.1.6. Salicylideneaniline-based COFs. The TFB-COF-Co-SA COF bearing single atomic Co sites and the structure mimicking the homogeneous complex $\text{Co}(\text{SA})_2$ formed by the coordination of Co^{2+} metal ions with the salicylideneaniline



(SA) ligand was synthesized. The TFBDCOF was made by reacting benzene-1,4-diamine (PDA) and 3,3',5,5'-tetraformyl-4,4'-biphenyldiol (TFBD) and was subsequently immobilized with Co^{2+} followed by coordination with the SA ligand to give TFBD-COF-Co-SA (Fig. 6g).⁹⁸ The photocatalytic performance was evaluated by dispersing the catalyst in MeCN and TEOA using $[\text{Ru}(\text{bpy})_3]\text{Cl}_2 \cdot 6\text{H}_2\text{O}$ as the PS. TFBD-COF-Co-SA leads to the CO production of $7400 \mu\text{mol g}^{-1}$ in 5 h with 90% selectivity. Notably, TFBD-COF-Co, which lacks an SA ligand coordinating group, shows a much inferior performance compared to TFBD-COF-Co-SA, which has a greater than four times CO evolution rate. Also, the CO evolution rate of TFBD-COF-Co-SA is comparable to the homogeneous molecular catalyst $\text{Co}(\text{SA})_2$ calculated based on the number of metal centres.

6.1.7. Multinuclear atomic cluster based COFs. The reports discussed here previously involve the incorporation of single metal sites or mononuclear complexes in the covalent organic framework. In this regard, it is fascinating to incorporate poly-nuclear metal complexes or atomically precise metal clusters owing to their structural diversity, synergistic effects among multiple active sites, and intriguing properties. Keeping this in perspective, a MOF \cup COF-type framework, namely MCOF- Ti_6Cu_3 , was designed by combining Ti-O clusters with oxidizing capability and Cu clusters with a reducing tendency to perform the CO_2RR and water oxidation simultaneously.⁹⁹ The presence of the active sites in close proximity promotes faster transport of electrons. The heterometallic MCOF- Ti_6Cu_3 catalyst was constructed by connecting the clusters through dynamic covalent linkage under relatively mild reaction conditions such that the intrinsic properties and structures of the individual clusters remain intact. The linkage facilitates rapid electron transfer and enhances synergistic interactions among the clusters. Notably, the photocatalytic reduction of CO_2 with the catalyst generates $20.4 \mu\text{mol}$ of HCOOH in 12 h and O_2 as the water oxidation product. In contrast, the precursors bearing the Ti_6 and Cu_3 clusters or the materials bearing single clusters, that is, MOF901 with Ti or FDM-71-ABC bearing Cu clusters, failed to perform the simultaneous CO_2 reduction and water oxidation. The mechanistic studies using *in situ* XPS and DFT studies support the transfer of electrons to the Cu cluster under light irradiation, which leads to the reduction and oxidation reactions at the Cu and Ti clusters, respectively.

In another report, the heterometallic hydrazone-linked COF (USTB-11(Cu,Ni)) was designed by incorporating the Cu_3 cluster and the post-synthetic treatment to incorporate Ni. USTB-11(Cu) was developed by the reaction of 4,4',4''-nitrilo-tribenzhydrazide (NTB-NH₂) and tris(μ 2-4-carboxaldehyde-pyrazolato- N,N')-tricopper (Cu_3Py_3) ($\text{Cu}_3(\text{PyCA})_3$) and the PSM with the Ni^{2+} ions generates USTB-11(Cu,Ni).¹⁰⁰ As a proof of concept, a metal-free analogue USTB-12 was also synthesized by the condensation of 1,3,5-tris(4-formylphenyl)benzene (TBZ-CHO) and NTB-NH₂ and further PSM with Ni^{2+} produces USTB-12(Ni). The heterometallic catalyst USTB-11(Cu,Ni) demonstrates a high CO production rate of $22\,130 \mu\text{mol g}^{-1} \text{ h}^{-1}$ with 98% selectivity, 7 times higher than USTB-12(Ni), highlighting the role of the synergy of Cu_3Py_3 and Ni in determining the catalytic

performance. In contrast, the other catalysts, USTB-11(Cu) and USTB-12, with only Cu clusters or no metal, show negligible photocatalytic activity. Mechanistic investigation with advanced spectroscopic techniques revealed the $\text{Cu}^{\text{I}}/\text{Cu}^{\text{II}}$ mixed oxidation state in the Cu_3Py_3 cluster with bistable $\text{Cu}_3^{4+}(\text{Cu}^{\text{I}}_2\text{Cu}^{\text{II}})$: $\text{Cu}_3^{5+}(\text{Cu}^{\text{I}}\text{Cu}^{\text{II}}_2)$ is greatly responsible for the improved catalytic performance, charge separation, and improved performance of Ni sites.

To further explore the role of linkage chemistry, a fully conjugated multivariate $-\text{C}=\text{C}-$ linked donor- π -acceptor MCOF, namely UJN-1, based on Cu cyclic trimer (Cu-CTU) sites was fabricated. UJN-1 was synthesized by the integration of 1,4-phenyldiacetonitrile (PDAN) with two different aldehyde precursors, electron-rich tris(4-formylphenyl)amine (TFPA) and an electron-deficient Cu_3L_3 cluster [*1H*-pyrazole-4-carbaldehyde (HL)]. This resulted in a robust structure with strong intramolecular charge separation due to the donor-acceptor moieties, extended conjugation, and abundant active sites. The meticulous design results in a high photocatalytic CO production rate of $114.8 \mu\text{mol g}^{-1}$ in 4 h without additional co-catalysts or sacrificial reagents.¹⁰¹ The mechanistic investigation revealed that the high performance is due to incorporating electron-deficient Cu-CTU that facilitates charge separation, accelerating photo-generated charge transfer from the electron-rich triphenylamine to Cu-CTU. A similar MCOF, UJN-2, with imine-linkage, and vinylene-linked COF UJN-3, lacking Cu-CTU moieties, show much lesser CO production of $28.9 \mu\text{mol g}^{-1}$ and $50.0 \mu\text{mol g}^{-1}$ underscoring the importance of charge separation driving force and the linkage in guiding the photocatalytic performance.

6.1.8. Metal ions intercalated between the COF layers. When the interlayer spacing of the COF layers is optimal and the chelating atoms in adjacent layers are appropriately aligned, metal ions can be effectively anchored within the interlayer space. A COF, DQTP, decorated with anthraquinone units, was designed, where various metal ions (M = Co, Ni, Zn) were coordinated due to the strong binding affinity of anthraquinone oxygen atoms, positioned at an optimal distance of 3.621 \AA . DQTP COF-Co gave the best CO production rate of $1.02 \times 10^3 \mu\text{mol h}^{-1} \text{ g}^{-1}$ and DQTP COF-Zn gave a high selectivity of 90% over HCOOH production.¹⁰² To decipher the role of the coordinating O atoms in the anthraquinone group, another COF DATP was synthesized by replacing the anthraquinone unit with the anthracene unit. As expected, DATP COF-M demonstrated inferior performance for CO_2 reduction, which can be attributed to its weak metal binding capabilities.

Furthermore, as discussed previously, a dual metalation strategy can be used to improve the catalytic performance of the COFs. A series of crystalline benzothiazole COFs (Co, Ni COF-*n*, *n* = 0,1,2,3, denoting the number of carbonyls in the as-synthesized COFs) were obtained by the reaction with benzene-1,3,5-tricarbaldehyde derivatives bearing various carbonyl groups to tune the photophysical properties.¹⁰³ DFT calculations revealed that the metal ions were coordinated in the interlayer spacing with metal-nitrogen interaction, and a spacing of 3.5 \AA was the optimized spacing. The photocatalytic



measurements revealed that CoNi COF-3 had the highest CO production rate of $2567 \mu\text{mol g}^{-1} \text{h}^{-1}$ with $\sim 92\%$ selectivity. The best performance is owing to the synergistic effect of the dual metallic sites and the formation of the β -ketoenamine structure in the COF that facilitates CO_2 adsorption, stabilizes the CO_2 reduction intermediate, and promotes charge separation.

In other materials, dual metalation can be done on the COF backbone and the interlayer spacing. The Co/Cu₃-TPA-COF was engineered by incorporating trinuclear Cu clusters in the COF structure linked by covalent bonds, and the single atomic Co sites are intercalated between the COF layers by anchoring on the imine-N moieties.¹⁰⁴ The Co centres are not only well dispersed and exposed within the COF channels but also promote oriented charge transfer from dual electron donors to Co sites, facilitating CO_2 reduction performance. The electron-withdrawing Cu^I/Cu^{II} centres in the Cu cluster and electron-rich amine site promote charge separation upon visible light illumination. This leads to effective induction of oriented electron transfer from the COF backbone to the intercalated Co-imine N sites, resulting in a high CO evolution rate of $25\ 247.7 \mu\text{mol g}^{-1} \text{h}^{-1}$ with $\sim 80\%$ selectivity.

Metal ions can interact synergistically with the COF structure, leading to new reaction pathways, enhanced stability, and increased durability under reaction conditions. However, like other metal-based COF photocatalysts, they are also prone to leaching of metal ions, degrading the performance. Also, achieving the structure necessitates complex design to promote intercalation between layers.

6.2. Encapsulating metallic catalysts in the COF pores

The high porosity, well-defined pore channels, and tunable micro-environments of COFs make them ideal scaffolds for confining various systems, including nanoparticles, polyoxometalates, and other homogeneous catalysts. Such confinement can significantly influence the chemical and physical properties of these systems through the synergistic effects between the confined catalyst and the porous frameworks.¹⁰⁵ The close spatial proximity between substrates and catalysts within COF pores facilitates increased reaction rates, improves the stability of homogeneous catalysts, and supports long term recyclability under the reaction conditions.¹⁰⁶ The catalysts can be confined in COF cavities through various interactions, including electrostatic, van der Waals, hydrogen, coordination, and covalent bonding.

6.2.1. Covalent anchoring of semiconductors. The limitations of noncovalent interactions in forming heterostructures can be addressed by functionalizing COFs with appropriate groups capable of anchoring other catalysts through stronger covalent linkages. Polyoxometalates (POMs) serve as an outstanding platform for catalysis due to their inherent redox activity. However, their catalytic performance is often hindered by limitations such as low porosity, inadequate light-harvesting capabilities, and a tendency to aggregate into larger particles during reactions.¹⁰⁷ To address these challenges, covalently anchoring POMs within COF nanopores offers a promising strategy to ensure uniform dispersion and enhanced stability. To achieve this, a subvalent [4+3] TTF-TAPT COF (TCOF) having

bex net topology was synthesized so there are unreacted aldehyde groups within the COF pores. The further Schiff base condensation with MnMo₆-2NH₂ bearing free amino groups generates a covalently anchored COF-POM composite TCOF-MnMo₆ (Fig. 7a).¹⁰⁸ Inspired by the visible light absorption, inherent catalytic sites, and charge transfer ability, the photocatalytic CO_2 reduction performance was measured under gas-solid conditions using CO_2 and water vapor without additional photosensitizers or sacrificial agents. The TCOF-MnMo₆ led to a CO production rate of $37.25 \mu\text{mol g}^{-1} \text{h}^{-1}$ with *ca.* 100% selectivity, while the pristine COF or POM showed negligible activity. Besides, the physical mixture TCOF/MnMo₆ and the POM@COF composite without covalent bonding showed much inferior performance. DFT studies suggested PET from the COF to the POM, which is responsible for water oxidation and CO_2 reduction.

Another example includes poly aryl ether (PAE) linked COF-316 and COF-318 bearing EWGs susceptible to nucleophilic attack by -OH groups. Utilizing this, they are covalently anchored with oxide semiconductors (TiO₂, Bi₂WO₆, and α -Fe₂O₃) having surfaces functionalized with hydroxy functionalities.¹¹¹ These inorganic catalysts are capable of water oxidation, while COF-316 and COF-318 can perform CO_2 photoreduction. Among all the synthesized catalysts, the COF-318-TiO₂ heterojunction catalyst showed the highest CO production rate of $69.67 \mu\text{mol g}^{-1} \text{h}^{-1}$ under gas-solid conditions without any external photosensitizer or SED, much superior to the pristine COF or TiO₂ catalysts or their physical mixture. Mechanistic investigations using DFT revealed that photogenerated charges are transferred from the semiconductor to the COF *via* covalent linkages and accumulate on the -CN/pyridine active sites of the COF backbone, which facilitates CO_2 reduction. Meanwhile, the holes remaining on the semiconductor drive water oxidation.

Leveraging the photocatalytic properties of both MOFs and COFs, a covalently tethered MOF-COF hetero-nanosheet (NZZ/TTCOF) was synthesized *via* a seed-mediated strategy.¹¹² The TTCOF was formed through an imine condensation reaction between TP and TAPT precursors, while the NZZ MOF nanosheets were prepared by coordinating 2-methylimidazole and 5-amino-1*H*-tetrazole with Zn nodes. The resulting heterostructure was achieved by covalently anchoring the COF onto the MOF nanosheets through C-N bonds within the keto-enamine framework of the TTCOF. NZZ exhibits UV responsiveness, while the TTCOF is responsive to IR radiation, enabling the heterostructure to achieve broad-spectrum light absorption capabilities. As expected, the NZZ/TTCOF hetero-nanosheet exhibits superior photocatalytic CO_2 reduction ability ($R_{\text{CO}} = 7.01 \mu\text{mol g}^{-1} \text{h}^{-1}$ and $R_{\text{CH}_4} = 2.50 \mu\text{mol g}^{-1} \text{h}^{-1}$) compared to both the pristine TTCOF and NZZ MOF, highlighting the role of forming heterostructures in improving the catalytic performance. Notably, this was achieved under gas-solid conditions without any external photosensitizer or co-catalyst.

Compared to the metallic active sites anchored through noncovalent linkages, the catalysts presented in the reports discussed above possess significant advantages. The metal atoms tend to leach over several cycles and are also known to



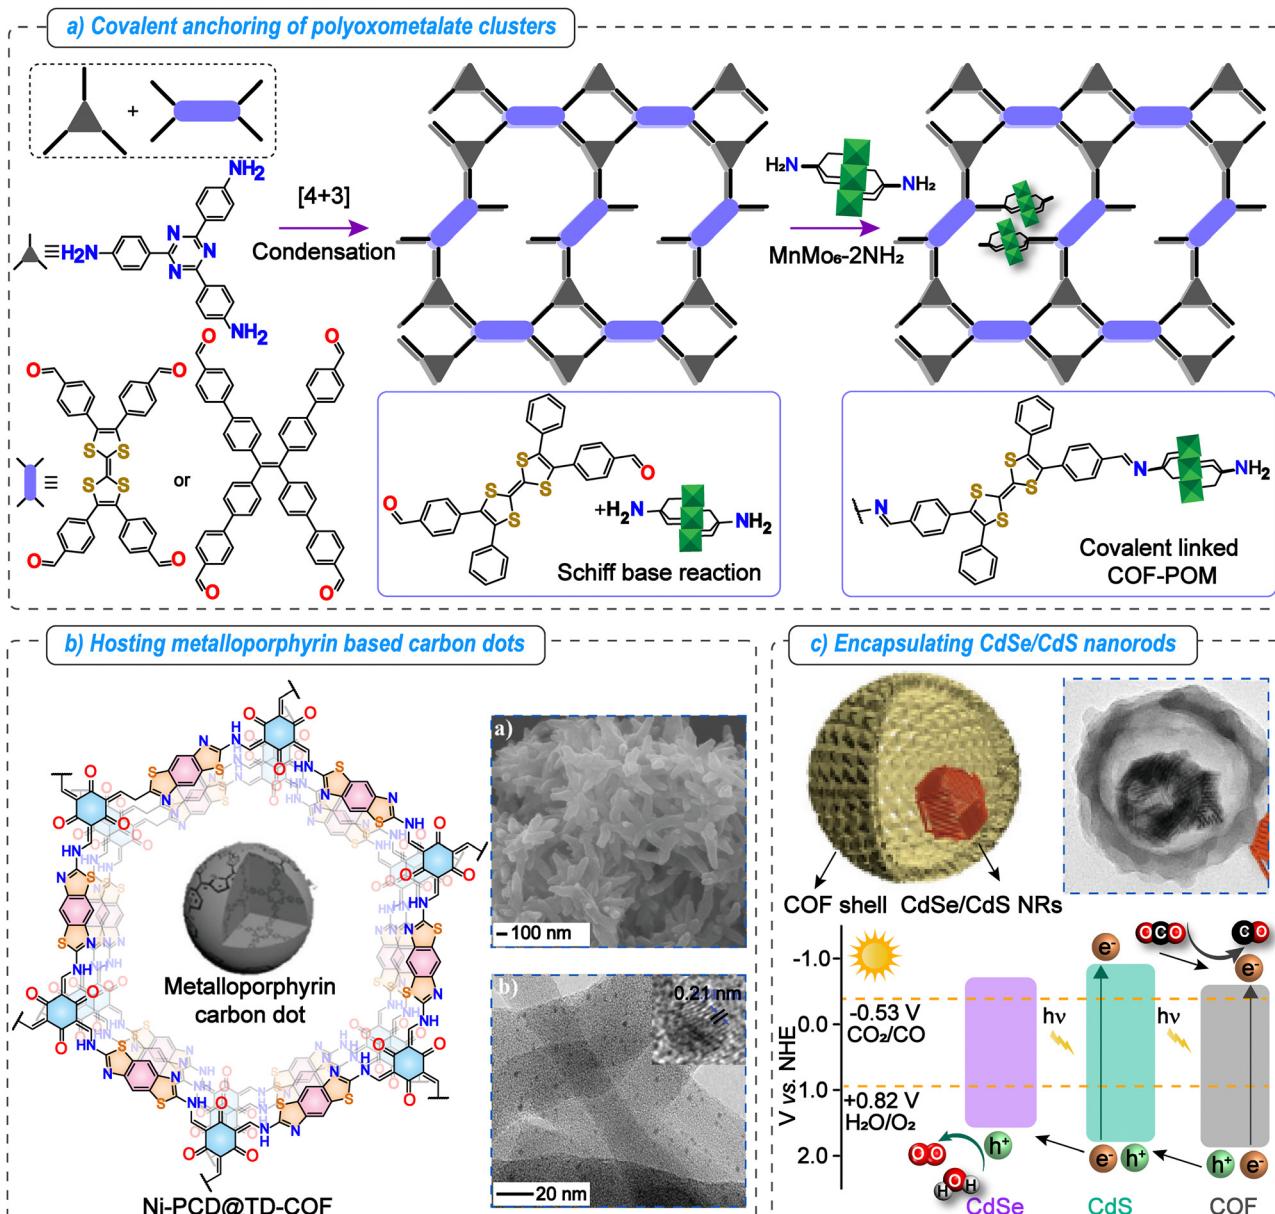


Fig. 7 Metalated COFs beyond single atom catalysts for photocatalytic CO₂ reduction. Key strategies to use the nanoconfinement effect of COFs. (a) Schematic illustration of covalent anchoring of polyoxometalate clusters in COF pores. (b) Hosting of metalloporphyrin-based carbon dots in a β -ketoenamine linked TD-COF. The SEM image indicates COF morphology and the TEM image indicates the uniformly dispersed carbon dots in the COF matrix. Adapted with permission from ref. 109, © 2020 Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim. (c) Schematic illustration and TEM image of the double-shelled structure formed by encapsulating CdSe/CdS nanorods in the COF. Band-structure diagram of TAPT-DMTA, CdS, and CdSe illustrating the plausible electron transfer pathway. Adapted with permission from ref. 110, Copyright © 2022, Hui Li et al.

coagulate into larger particles degrading the catalytic activity over time. In contrast, covalent anchoring of the semiconductor is an important development in the direction of overcoming this limitation. However, this requires sophisticated designs which can be sometimes complex to synthesize.

6.2.2. Hosting metalloporphyrin carbon dots. Incorporating metal anchoring building blocks like porphyrin and bipyridine is a viable strategy for designing heterogeneous catalysts with high efficiency and recyclability for photocatalytic CO₂ reduction. However, this requires specialized COF designs.

In this regard, a more general approach is utilizing the COF pores for encapsulating metalloporphyrin-based carbon dots. To achieve this, the TD-COF was synthesized by the reaction of 2,4,6-triformylphloroglucinol (TP) and 2,6-diaminobenzo[1,2-*d*:4,5-*d'*]bisthiazole (DBT) and the subsequent treatment with nickel 5,10,15,20-tetrakis(*p*-tetraphenylamino)porphyrin (Ni-TPAP) and glucose, followed by selectively pyrolyzing glucose in an inert atmosphere at 200 °C, generating the Ni-PCD@TD-COF (Fig. 7b).¹⁰⁹ The photocatalytic CO₂ reduction using the Ni-PCD@TD-COF catalyst, [Ru(bpy)₃]Cl₂ as the photosensitizer,



and TEOA as the SED demonstrate a CO production of $956 \mu\text{mol g}^{-1}$ in 2 h with 98% selectivity. Interestingly, the material showed good photoactivity in the simulated flue gas atmosphere (0.15 atm CO₂ and 0.85 atm N₂), which was attributed to the enhancement in the local CO₂ concentration due to selective CO₂ capture by the photosystem.

6.2.3. Immobilizing metallic nanoparticles. The porous COFs can be used to immobilize various nanomaterials like CdSe/CdS nanorods, TiO₂, Ru, Ni, and Fe nanoparticles in the micro- and mesopores, which can subsequently enhance the catalytic performance.¹¹³ For example, the self-assembly of a well-known chalcogenide photocatalyst CdSe/CdS nanorods (NRs) and COFs results in core–shell inorganic–organic hybrid structures (Fig. 7c). Although colloidal quantum dots are active towards CO₂ photoreduction, their non-porous structures lead to poor CO₂ adsorption, compromising their reduction efficiency. The integration of COFs with CdSe/CdS nanorods (NRs) enhances both adsorption and conversion, making them a highly promising candidate. The core of NRs is in close proximity to the COF shell, facilitating the PET from the NR to COF. The hybrid structure showed a high photocatalytic CO₂ to CO production rate of $64.6 \mu\text{mol g}^{-1} \text{ h}^{-1}$ under solid–gas conditions, far superior to the parent COF or NRs under the reaction conditions.¹¹⁰ In another report, the CdS@COF core–shell structure was engineered to overcome the strong polarizing effects of the heteroatom-containing imine linkages, which lead to poor π -electron delocalization.¹¹⁴ This, in turn, gives poor photocatalytic efficiency due to low intramolecular electron transfer. The integration of the imine COF bearing Zn-porphyrin and Co-bipyridyl functionalities with CdS nanowires provided an efficient electron transfer channel inducing PET from Zn-porphyrin to CdS, which subsequently transfers to the Co-bipyridyl units, where the CO₂ reduction takes place. This leads to the CO production of $4057 \mu\text{mol g}^{-1}$ in 8 h, bypassing the performance of the CdS or COF congeners.

The selective photocatalytic reduction of CO₂ to HCOOH was obtained by immobilizing Ru nanoparticles ($\sim 8 \text{ nm}$) in a β -ketoenamine-linked Tp-Pa1 COF.¹¹⁵ Like the previous cases, forming an organic–inorganic composite structure facilitated broader light absorption and electron transfer through the Ru NPs. 3.0 wt% Ru/TpPa-1 demonstrated the highest HCOOH yield of $108.8 \mu\text{mol g}^{-1} \text{ h}^{-1}$, superior to Tp-Pa1 ($32.4 \mu\text{mol g}^{-1} \text{ h}^{-1}$). Likewise, the role of the semiconductor facet in determining the photocatalytic efficiency was highlighted by synthesizing 101-TiO₂/COF and 001-TiO₂/COF heterostructures.¹¹⁶ It was found that 101-TiO₂/COF, having an electron-rich nature and a relatively lower conduction band than 001-TiO₂/COF, showed a higher CO₂ reduction efficiency with a CO production rate of $11.6 \mu\text{mol h}^{-1}$. In contrast, the CO production rates of 101-TiO₂ and 001-TiO₂/COF were 0.8 and $2.5 \mu\text{mol h}^{-1}$, respectively.

The immobilization of inorganic nanoparticles with organic COF supports presents an interesting platform for enhancing CO₂ photoreduction efficiency. However, with long-term use, the crystallinity of the COFs tends to degrade, leading to potential metal leaching. Additionally, the nanoparticles are susceptible to coagulation over multiple cycles, which can

undermine the overall performance. To address this critical challenge, further research is required to improve the design.

Thus, metalated COF-based catalysts for photocatalytic CO₂ reduction offer several advantages, making them highly effective in converting CO₂ into value-added products. The well-defined pore structures and tunable linkers, linkages, and morphologies of COFs allow precise incorporation of metal active sites, enhancing catalytic efficiency and providing greater synthetic flexibility. This structural control not only improves metal accessibility, reducing the overall metal requirement, but also facilitates catalyst recyclability. When incorporated into porous materials like COFs, these metal sites become more accessible, reducing the overall metal requirement and enhancing recyclability. Additionally, the protective environment of COFs stabilizes the metal centres, prolonging the catalyst lifetime and maintaining activity over multiple cycles. However, metal-based catalysts also have notable limitations. One major drawback is metal leaching, which leads to a decline in catalytic performance over time. Furthermore, the reliance on noble metals, such as Pt or Ru, increases costs and reduces the sustainability of large-scale applications.

6.3. Metal-free COFs as heterogeneous catalysts for photocatalytic CO₂ reduction

COFs constructed from π -conjugated building blocks offer an excellent platform for developing metal-free photocatalysts for CO₂ reduction reactions (CO₂RR). These frameworks can be enriched with heteroatoms, such as nitrogen (N), sulfur (S), and phosphorus (P), which serve as active sites for CO₂ adsorption and subsequent conversion. The heteroatoms facilitate CO₂ activation by inducing polarization through dipole–quadrupole interactions.

Furthermore, the extended π -conjugation in these materials enhances visible-light absorption, while their donor–acceptor architecture promotes efficient charge separation and prolongs the lifetime of photoexcited electrons. Various photoactive moieties, such as eosin Y, pyrene, and perylene, have been incorporated into the COF or porous organic polymer (POP) backbones to enhance visible-light responsiveness.^{117,118} Additionally, triazine-based linkers, which feature abundant nitrogen sites, have shown significant potential for CO₂ activation. This section highlights key design strategies to develop metal-free COF-based systems for photocatalytic CO₂ reduction.

6.3.1. Donor–acceptor-based systems. In general, the organic photocatalysts have a small Frenkel exciton radius of $\approx 5 \text{ \AA}$. Additionally, the Coulomb binding energy of the excitons is large and in the range of 0.3–1.0 eV, which restricts charge separation, thereby impeding the photocatalytic efficiency.¹¹⁹ A pivotal strategy to improve their efficiency is constructing a donor–acceptor (D–A) system based on an electron-rich donor unit and an electron-deficient acceptor unit. These materials have large dipole moments owing to the disparate electron affinity potentials, which facilitate the photoinduced electron transfer from the donor to the acceptor. Moreover, they have narrow band gaps, leading to a redshift of the absorption edge, facilitating broader light harnessing. Keeping this in perspective, an imine-linked DA



COF (CT-COF) was designed by integrating electron-rich carbazole (9-ethyl-9*H*-carbazole-2,7-dicarboxaldehyde (CZ)) and acceptor triazine (TAPT precursor) moieties (Fig. 8a). The DA-based design leads to a high efficiency of photocatalytic CO_2 reduction with a

CO production rate of $102.7 \mu\text{mol g}^{-1} \text{ h}^{-1}$ with at least 98% selectivity without using any external co-catalysts.¹²⁰ It is worth noting that the CO_2 photoreduction was done using water vapor since the band position was suitable for water oxidation. Notably,

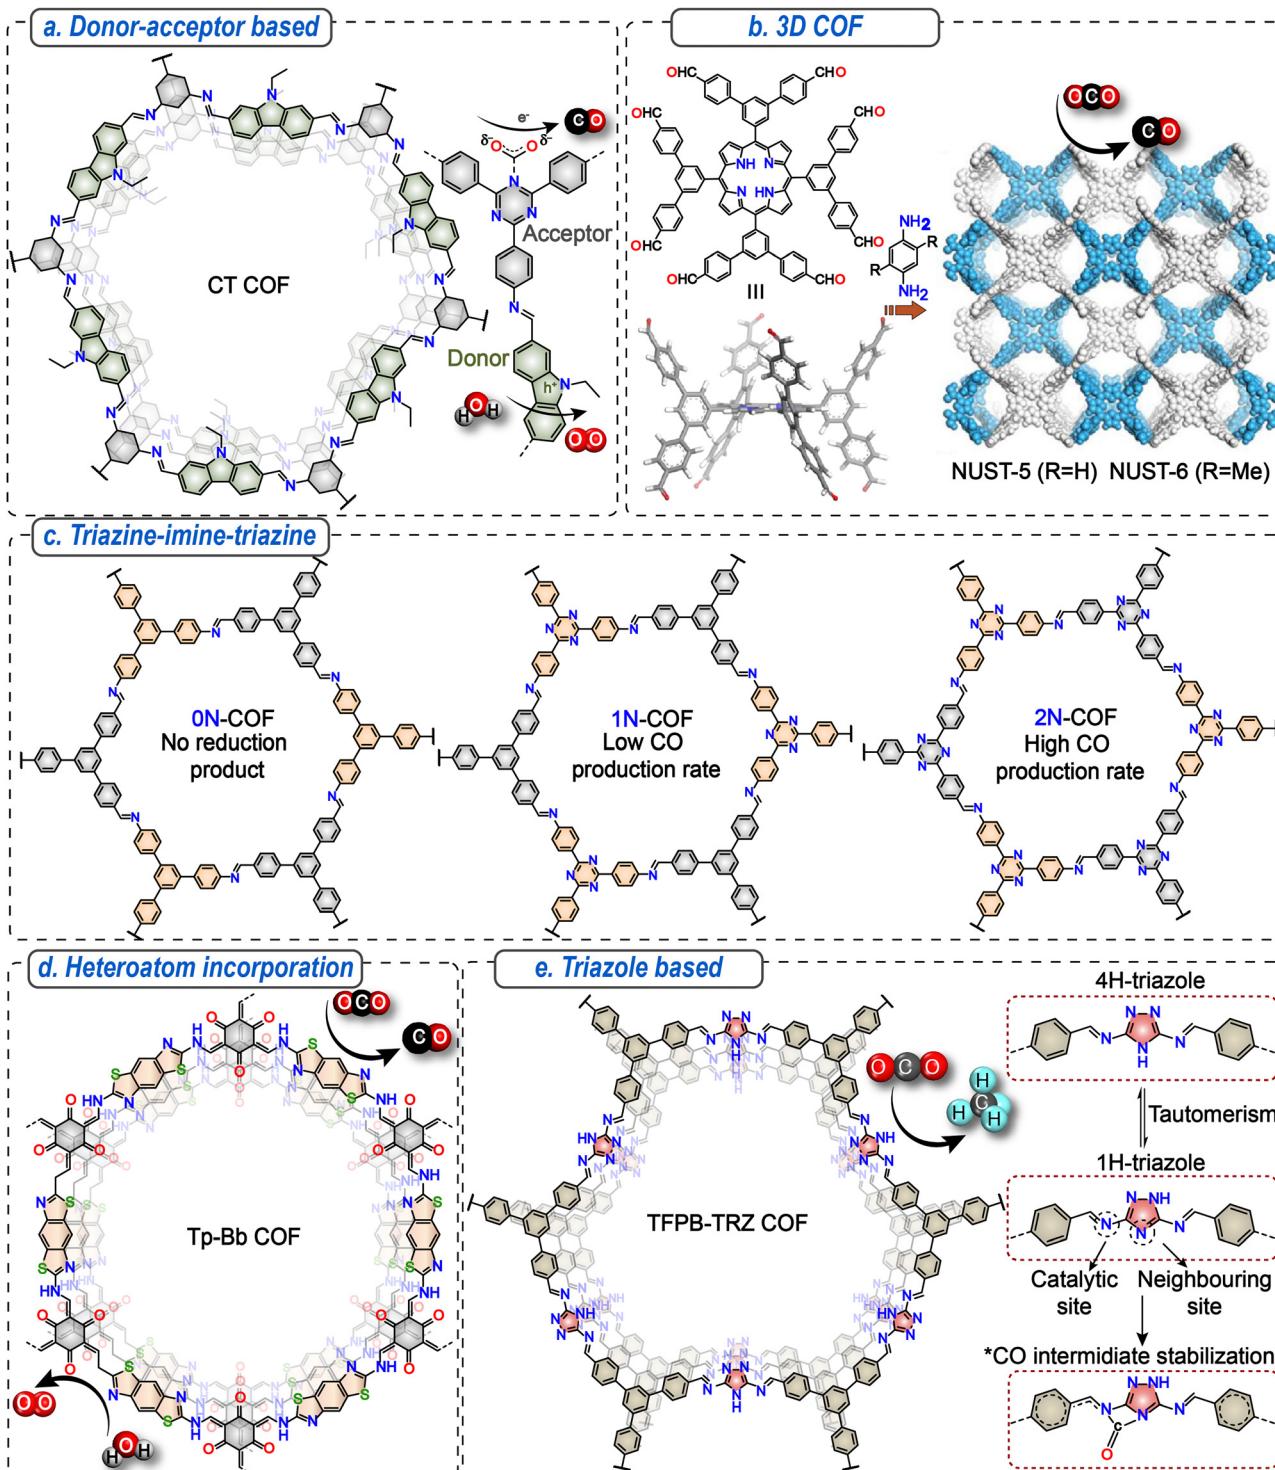


Fig. 8 Key strategies to develop metal-free COFs for photocatalytic CO_2 reduction. (a) Formation of a donor–acceptor structure, (b) design of 3D structure, adapted with permission from ref. 121, Copyright © 2022, American Chemical Society. (c) Fabricating COF membranes with the triazine–imine–triazine linkage, (d) incorporation of heteroatoms, and (e) triazole-based system.



the amorphous polymer bearing a similar chemical structure to the CT-COF exhibited inferior performance ($43.4 \mu\text{mol g}^{-1} \text{h}^{-1}$), underscoring the importance of crystallinity in determining the catalytic efficiency. The work highlights how the band position of the COF can be tuned to overcome the challenge of water oxidation, reducing the dependence on sacrificial agents. Such a system can also overcome the challenge of product overestimation due to the decomposition of the SEDs.

6.3.2. Construction of 3D COFs. The multidirectional interconnected networks render active sites more accessible in 3D COFs compared to 2D COFs. The higher surface area promotes the facile diffusion of substrates leading to improved reactant transfer, which can enhance photocatalytic performance. Two imine-linked 3D COFs (NUST-5 and NUST-6) with *pcb* topology were synthesized using octatopic 8-connected porphyrin-based aldehyde and diatopic amines (Fig. 8b).¹²¹ Inspired by the suitable band positions and the presence of several π -conjugated porphyrin units, the photocatalytic CO_2 reduction performance of these COFs was measured by dispersing the catalyst in an MeCN and water mixture using TEOA as the SED under metal-free conditions. NUST-5 and NUST-6 showed the CO production rates of 54.7 and $76.2 \mu\text{mol g}^{-1}$ and CH_4 production rate of 17.2 and $12.8 \mu\text{mol g}^{-1}$ in 10 h , respectively, demonstrating the use of 3D COFs for photocatalytic applications.

6.3.3. Fabricating COF membranes with the triazine-imine-triazine linkage. The macromolecular architecture of COFs plays an important role in determining the properties of the materials based on similar building blocks. In this regard, Wang and co-workers have shown the superior photocatalytic performance of COF membranes over the commonly used COF powders under gas-solid conditions. A series of imine-linked COFs, *XN*-COFs (*X* = 0, 1, or 2 based on the number of triazine moieties in the repeating unit), were synthesized by varying the number of N heteroatoms (Fig. 8c).¹²² Increasing the number of triazine groups enhanced the crystallinity, porosity, CO_2 uptake, and band gap of the materials due to the rigid and planar structure of triazine that promotes interlayer stacking. Accordingly, the photocatalytic CO_2 reduction studies show that the 2*N*-COF bearing the triazine-imine-triazine linkage has the highest CO production rate of $310 \mu\text{mol g}^{-1} \text{h}^{-1}$, without additives. Notably, for the same 2*N*-COF, the membrane form showed a 3.2 times higher rate over the powdered material. The membrane form is shown to have better charge separation and transfer and enhance reaction kinetics, reflected in the catalytic performance. The work highlighted the role of chemical structure and macroscopic architecture in determining photocatalytic performance. More studies are required in this direction to completely understand the role of macroarchitecture in guiding the photocatalytic performance.

6.3.4. Heteroatom incorporation. The precursors decorated with heteroatoms like S can have a profound impact on the photocatalytic performance of the material. The polarisable atoms tend to enhance the CO_2 uptake and charge carrier mobility. In this regard, a β -ketoenamine linked COF was designed by the reaction of Tp aldehyde and S containing 2,6-diaminobenzo[1,2-*d*:4,5-*d'*]bisthiazole (Bb-NH₂) amine linker to

give the TpBp COF (Fig. 8d).¹²³ The COF exhibited a high CO production rate of $52.8 \mu\text{mol g}^{-1} \text{h}^{-1}$ with 99% selectivity at 80°C . A similar β -ketoenamine-linked COF Tp-Pa1 without any S heteroatoms showed a much lower CO evolution rate of $18.3 \mu\text{mol g}^{-1} \text{h}^{-1}$. Also, the rate was 2.3 times ($23.2 \mu\text{mol g}^{-1} \text{h}^{-1}$) that of a well-known metal-free photocatalyst, graphitic carbon nitride ($\text{g-C}_3\text{N}_4$). Notably, under 30% diluted CO_2 , a much higher CO generation rate of $89.9 \mu\text{mol g}^{-1} \text{h}^{-1}$ was obtained, indicating that lower CO_2 concentration is more favorable towards CO_2 reduction.

Another study demonstrated the effect of bromine moiety incorporation on modulating the bandgap for improving photocatalytic performance. COF-366, designed from the condensation of 5,10,15,20-tetrakis(4-aminophenyl)porphyrin (TAPP) and terephthalaldehyde, doesn't have an appropriate band position for the water oxidation reaction. To overcome this limitation, bromine was incorporated into the building unit to design the TAPBB-COF by condensing TAPP with 2,5-dibromo-terephthalaldehyde (BDB).¹²⁴ The TAPBB-COF demonstrated a CO generation rate of $24.6 \mu\text{mol g}^{-1} \text{h}^{-1}$ with greater than 95% selectivity, about 3 times higher than COF-366 and 1.5 times over $\text{g-C}_3\text{N}_4$. Introducing Br sites shifts the VB to a more positive position, promoting the water oxidation reaction. DFT calculations support the role of the N atoms of the porphyrin ring and imine group and the Br atoms in enhancing CO_2 activation and conversion with water in the photocatalytic reaction.

6.3.5. Triazole-based COFs. The most common photocatalytic CO_2 reduction product in COF-based materials is preferentially CO, likely due to the weak binding of the *CO species, which is a key intermediate in producing higher-order products. A pathway to achieving this is to incorporate a neighboring group capable of donating electrons that can satiate the π -acceptor ability of the CO group. Reticular chemistry offers structural tailorability, thereby allowing the precise selection of building blocks capable of stabilizing the *CO intermediate. In this regard, an 8e^- reduction of CO_2 to CH_4 was achieved under metal-free conditions by designing a triazole-based TFPB-TRZ COF (Fig. 8e).¹²⁵ Multiple N heteroatoms in the triazole ring promote high CO_2 uptake and visible light absorption, providing an appropriate band gap for photocatalysis. The photocatalytic CO_2 reduction gave CH_4 at a rate of $128 \mu\text{mol g}^{-1} \text{h}^{-1}$ with 99% selectivity using 1-benzyl-1,4-dihydronicotinamide (BNAH) and triethylamine (TEA) as sacrificial agents in 2:1 MeCN:H₂O solvent. Even in direct sunlight, an excellent CH_4 production rate of $61.62 \mu\text{mol g}^{-1} \text{h}^{-1}$ was achieved. DFT calculations showed that the presence of 1,2,4-triazole sites in the COF backbone stabilizes the *CO intermediate through electron donation, thereby assisting the multielectron reduction of CO_2 . The triazole species exists in an equilibrium between tautomerie forms 1*H*-triazole and 4*H*-triazole that can be interconverted via weak bases, like, in this case, TEA. This is also supported experimentally as the absence of TEA and using only BNAH as a sacrificial agent lead to poor catalytic performance. 1*H*-Triazole plays an active role in stabilizing the *CO intermediate.



6.3.6. Water affinity modulation. Water acts as a hydrogen and electron source when performing CO_2 photoreduction in the aqueous medium. The presence of ample water molecules adjacent to the catalytic sites can enhance the local concentration of CO_2 and act as electron donors, promoting CO_2 photoreduction efficiency. For example, the presence of hydrophilic sites in natural photosystem II attracts the water molecules *via* H bonding, facilitating electron donation and, therefore, water oxidation. Inspired by this, Jin *et al.* designed a fully conjugated QL-COF with pores decorated with hydrophilic $-\text{COOH}$ groups by the Doebner reaction between 1,3,5-triformylbenzene and 1,4-diaminobenzene.¹²⁶ As a proof of concept, a similar imine-linked LZU1-COF was synthesized by Schiff base condensation between the same precursors. The QL-COF featured superior H_2O uptake that subsequently promoted CO_2 adsorption over the LZU1-COF. Moreover, the extended conjugation promoted photoexcited charge separation and transfer, leading to a high CO production rate of $156 \mu\text{mol g}^{-1} \text{h}^{-1}$ with 99.3% selectivity in the QL-COF in comparison to a rate of $25 \mu\text{mol g}^{-1} \text{h}^{-1}$ in the LZU1-COF. The work provides important insights into designing catalysts with high CO_2 reduction and water oxidation activity.

Building on the previous discussion, COFs offer exceptional structural tunability, which enables the design and optimization of systems for photocatalytic CO_2 reduction. Their environmental friendliness and sustainability further enhance their potential for future applications. Recent efforts have focused on performing these reactions in an aqueous medium, which significantly increases their practical appeal. The structural tunability of COFs allows for the design of materials with high selectivity, minimizing the competing hydrogen evolution reaction. Reticular chemistry is employed to adjust the band gap and facilitate charge transfer, addressing the challenge of water oxidation. Additionally, the reduced reliance on sacrificial agents helps prevent the overestimation of CO_2 reduction products. Many studies have incorporated isotopic labeling with $^{13}\text{CO}_2$ to confirm the source of reduction products and eliminate the possibility of products stemming from secondary electron donors (SEDs). *In situ* techniques like DRIFTS provide valuable insights into the active intermediates formed during the reduction process. As previously mentioned, the presence of extended conjugation in COFs positions them as promising candidates for overcoming the reliance on metals. However, the field is still in its early stages, and the efficiency of metal-free catalysts must be further improved to meet industrial standards.

7. Structure–property relationship in reticular materials for modulating photocatalytic CO_2 reduction

The photocatalytic CO_2 reduction performance of a material, characterized by its efficiency and selectivity, is governed by a complex interplay of various material properties, including CO_2

uptake capacity, intermediate stabilization, light-harvesting ability, band alignments, structural stability, and accessibility to active sites. Understanding the structure–property relationship is crucial for optimizing photocatalytic activity. For instance, the accessibility of active sites significantly influences catalytic efficiency; however, despite high porosity, strong interlayer stacking in certain COFs may hinder access to deeply buried active sites.¹²⁷ Developing strategies to enhance active site accessibility remains a critical area of research.

Covalent organic frameworks (COFs) offer exceptional structural tunability, where minor structural modifications can drastically impact reaction rates, product selectivity, and catalytic efficiency. Researchers can optimize critical parameters such as adsorption, activation, charge transport, and product specificity by systematically leveraging this tunability. Although understanding the structure–property relationship in COFs is still in their nascent stage, significant efforts have been made to identify the parameters affecting photocatalytic performance. This section provides an overview of how subtle structural modifications in reticular materials guide their photocatalytic performance, offering insights into the design and development of advanced catalysts for CO_2 reduction.

7.1. Spin-state manipulation of the metal active sites

The N_4 binding pockets in the porphyrin are apt for binding various metal ions and are capable of modulating the catalytic performance. Jiang and co-workers have shown that for the same metal ion, manipulation of the oxidation state, and hence the spin state, can profoundly impact selectivity and efficiency. To demonstrate this, COF-367-bearing cobalt-porphyrin groups with Co^{II} and Co^{III} having a spin state of $S = 1/2$ and 0 spin ground states, respectively, were synthesized (Fig. 9a).¹²⁸ The evaluation of photocatalytic CO_2 reduction depicts almost similar production rates (in $\mu\text{mol g}^{-1} \text{h}^{-1}$) of HCOOH (48.6 ± 9.2), CO (16.5 ± 1.9), and CH_4 (12.8 ± 1.9) in the material bearing Co^{II} (COF-367-CoII). In contrast, COF-367-Co^{III} demonstrates a highly selective HCOOH production rate of $93.0 \pm 4.63 \mu\text{mol g}^{-1} \text{h}^{-1}$. At the same time, a negligible amount of CO and CH_4 is produced, indicating the role of spin state modulation in guiding the photocatalytic activity and selectivity. COF-367 doesn't show any photocatalytic CO_2 reduction, highlighting the role of Co active sites. Notably, the precursors Co^{II} -TAP and Co^{III} -TAP show much lower activity towards HCOOH production, suggesting activity enhancement during the periodic assembly of the multiple Co-TAP units in the COF. The photoelectrochemical measurement shows that the spin state is essential in determining charge separation efficiency, which follows the order of COF-367-Co^{III} > COF-367-Co^{II} > COF-367. Theoretical insights using DFT suggest that strong binding of CO_2 and HCOOH in COF-367-Co^{III} over COF-367-Co^{II} ultimately translates into high selectivity and activity. The first step involves CO_2 binding through the formation of a Co–O bond, and the calculations show higher binding energy and a smaller bond length in COF-367-Co^{III} over COF-367-Co^{II}, suggesting stronger binding with COF-367-Co^{III}. The more favorable binding energy results from the spin state of the central cobalt ion,



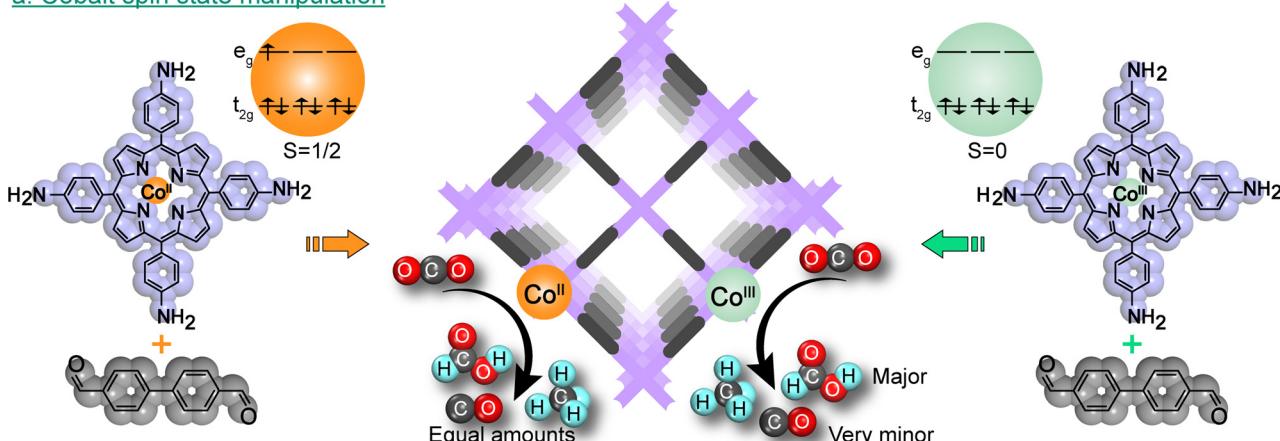
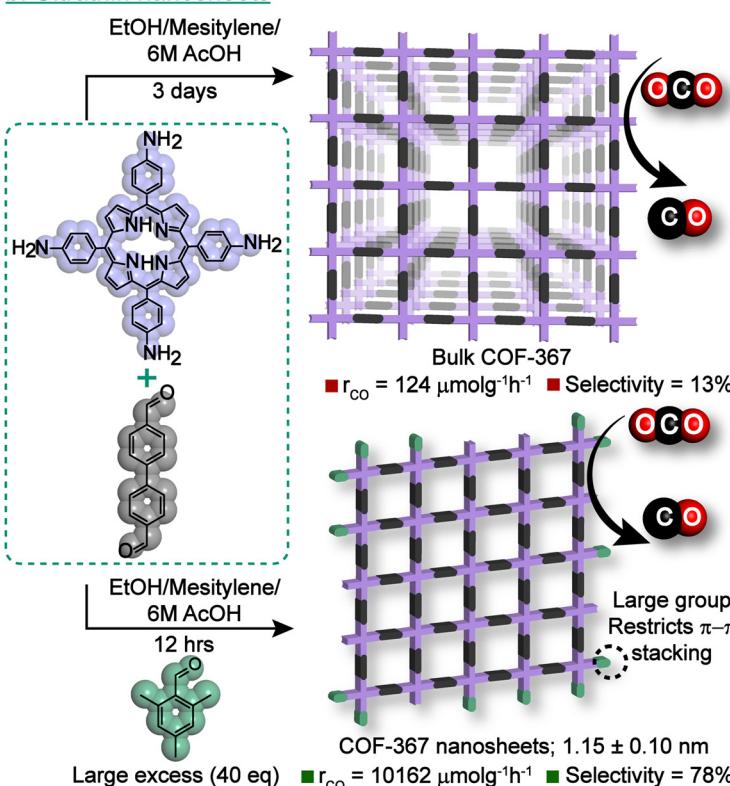
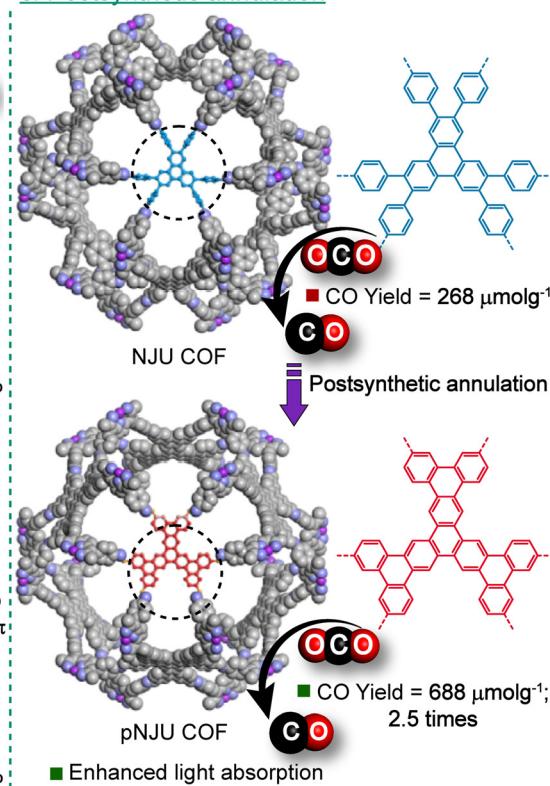
a. Cobalt spin state manipulationb. Ultrathin nanosheetsc. Postsynthetic annulation

Fig. 9 Structure–property relationship in reticular materials for modulating photocatalytic CO_2 reduction. (a) Schematic illustration to show the effect of spin state modulation of the active metal centre to tune the photocatalytic efficiency and selectivity. (b) Delamination of bulk COFs into ultrathin nanosheets to modulate photocatalytic efficiency and selectivity. (c) Postsynthetic annulation to modulate the photophysical properties to improve photocatalytic performance. Adapted with permission from ref. 121, Copyright © 2023, American Chemical Society.

wherein in Co^{II} with $S = 1/2$, $\text{Co}-3\text{d}_{xz}$ or $\text{Co}-3\text{d}_{yz}$ couples with $\text{O}-2\text{p}$. Meanwhile, for COF-367- Co^{III} , $\text{Co}-3\text{d}_{z^2}$ overlaps with $\text{O}-2\text{p}$, resulting in a much stronger orbital interaction. The further conversion of adsorbed CO_2 to HCOOH proceeds through two hydrogenation steps, which are more favorable for COF-367- Co^{III} over COF-367- Co^{II} , supporting its higher activity towards HCOOH production. The subsequent conversion of HCOOH to CO and CH_4 is energetically more favorable in COF-367- Co^{II} , accounting for the poor selectivity. The work highlights the role of reticular chemistry in promoting structural changes that can

reciprocate towards guiding the product selectivity and catalytic activity.

7.2. Dimensionality modulation

The rigid and planar building blocks of 2D COFs lead to strong interlayer stacking, limiting active site accessibility. Likewise, most 3D COFs are based on tetrahedral building blocks restricting structural diversity and functional regulation. Besides, interpenetration in these materials leads to decreased porosity and smaller pore sizes, which are detrimental to catalysis.



In this context, Fang *et al.* synthesized an stp-topologized 3D COF JUC-640-M (M = Co, Ni, or H) based on D_{3h} triptycene and metalloporphyrin building blocks.¹²⁹ The large surface areas and interconnected pore channels in this 3D COF make the active porphyrin sites more accessible and exposed. Inspired by this, the photocatalytic CO_2 reduction studies were performed in an $MeCN:H_2O = 2:3$ mixture utilizing BIH as the SED and $Ru(bpy)_3Cl_2 \cdot 6H_2O$ as the photosensitizer. This results in high photocatalytic CO_2 conversion to CO $15.1 \text{ mmol g}^{-1} \text{ h}^{-1}$ with more than 94% selectivity in JUC-640-Co.

The 2D imine-linked COFs suffer from poor charge transfer efficiency due to the polarization of the imine linkage, which increases the energy barrier for electron delocalization and leads to low efficiency without external photosensitizers. To overcome this limitation, Cao and co-workers developed 1D pyrene-based COFs bearing dual-chain-like edge architectures. The 1D PyTTA-COF-Co demonstrated a CO evolution of $1003 \text{ } \mu\text{mol g}^{-1}$ in 8 h, over 59 times higher than the 2D congener, highlighting the role of dimensionality in determining the catalytic efficiency.¹³⁰ Insights from the experimental observations and theoretical calculations show that 1D structures reduce exciton dissociation and thermal relaxation of photoelectrons, thereby improving photocatalytic efficiency.

However, research on 3D and 1D COFs for photocatalytic CO_2 reduction is still in its nascence and more research is required to unlock their full potential.

7.3. Improving the active site accessibility

As discussed earlier, 2D COFs suffer from mass transfer limitations due to their strong interlayer stacking. A way to overcome this limitation is to increase the interlayer stacking distance. A series of 2D porphyrin-decorated COFs were synthesized by the reaction of porphyrin aldehyde MPor-CHO (M = H₂, Co, and Ni) with 3,8-diamino-6-phenylphenanthridine (DPP).¹³¹ The presence of a bulky phenyl linker in the DPP amine leads to a high interlayer distance of 6 Å in the MPor-DPP-COFs. Consequently, the CoPor-DPP-COF showed a high Co generation rate of $10200 \text{ } \mu\text{mol g}^{-1} \text{ h}^{-1}$ with 82% selectivity. In contrast, COF-367-Co, having a similar Co active site but smaller interlayer spacing, showed a much inferior CO production rate of $5560 \text{ } \mu\text{mol g}^{-1} \text{ h}^{-1}$ with reduced selectivity of 78%, highlighting the importance of interlayer spacing in guiding the performance.

Another vital strategy in this context is the delamination of bulk COFs to produce ultrathin covalent organic nanosheets (CONs). Compared to the stacked 2D counterparts, CONs with minuscule thickness boast higher accessible sites, leading to shorter diffusion pathways. Besides, they are more processable than bulk COFs and can be dispersed well in several organic solvents. Taking advantage of these features in CONs, Jiang *et al.* developed a series of CONs with thickness $< 2.1 \text{ nm}$ through a bottom-up imine exchange strategy. To achieve this, an excess amount of bulky 2,4,6-trimethylbenzaldehyde was added to the reaction mixture that reacted along the edges during COF crystallization, hindering the $\pi-\pi$ stacking and growth along the z direction.¹³² Notably, COF-367-Co NSs

demonstrate a high CO production rate of $10162 \text{ } \mu\text{mol g}^{-1} \text{ h}^{-1}$ with 78% selectivity, exceeding the bulk counterpart that showed a far inferior CO production rate of $124 \text{ } \mu\text{mol g}^{-1} \text{ h}^{-1}$ with a selectivity of only 13% under similar conditions, highlighting the importance of NSs in improvising the performance (Fig. 9b). Likewise, Cooper and co-workers designed a series of CONs with Co active sites coordinated through the iminopyridine functionality for photocatalytic CO_2 reduction. The Co-FPy-CONs with fluorine to enhance the CO_2 uptake showed CO production of $10.1 \text{ } \mu\text{mol}$ with 76% selectivity in 6 h, 4.3 times higher than the bulk Co-FPy-COF, which might be partially due to lower Co loading.¹³³ The Co-Py-CON produced a less CO of $7.4 \text{ } \mu\text{mol}$ in 6 h but was again higher than the bulk material.

7.4. Post-synthetic annulation

The prerequisite of photocatalytic activity is efficient light harnessing. Introducing highly conjugated building units into the COF backbone is instrumental in light absorption, but it is limited by the poor solubility of the precursors hindering COF crystallization. Post-synthetic annulation is an intriguing approach to enhance the light harnessing and stability, thereby enhancing the photocatalytic activity of the resulting material. Compared to 2D COFs, 3D COFs serve as suitable platforms for post-synthetic functionalization owing to their more exposed sites and interconnected pore channels. A 3D COF, NJU-319Fe, was synthesized by connecting hexaphenyl-triphenylene and Fe-porphyrin-based building units.¹³⁴ Interestingly, hexaphenyl-triphenylene was post-synthetically cyclized into higher π -conjugated hexabenzocoronene, generating the pNJU-319Fe COF, using intramolecular oxidative cyclodehydrogenation, commonly known as the Scholl reaction under mild conditions (Fig. 9c). As expected, the PSM enhanced visible light absorption reflected in the photocatalytic CO_2 reduction performance. The pNJU-319Fe COF showed a CO evolution of $688 \text{ } \mu\text{mol g}^{-1}$ in 10 h, 2.5-fold higher than the pristine NJU-319Fe ($268 \text{ } \mu\text{mol g}^{-1}$) under similar conditions. The study highlights the role of small structural tunability that can profoundly impact the overall material performance.

7.5. Electronic property modulation

Imine chemistry has been widely explored for developing COF photocatalysts for the CO_2 RR. Interestingly, the linkage direction, *i.e.*, whether the imine linkage is forward (f) or reversed (r) in isomeric COF structures, can have a profound impact on determining the catalytic performance. Four imine-linked COFs incorporating bipyridine and triazine groups were designed, both in their metal-free and Re-metalated forms. These COFs featured distinct linkage orientations designated as the f-COF, Re-f-COF, r-COF, and Re-r-COF.¹³⁵ The isomeric Re-r-COF (7.4% Re) and Re-f-COF (6.2% Re) have distinct photocatalytic performance. The Re-f-COF shows a CO generation rate of $6.3 \pm 1.2 \text{ mmol g}^{-1}$ in 8 h, while the Re-r-COF gives only $0.30 \pm 0.05 \text{ mmol g}^{-1}$ in the same duration. The drastic change in the behavior is attributed to the change in the photophysical properties of the structure. 2,2'-Bipyridine behaves as an electron-donating group in the r-imine, while it



switches to an electron acceptor in the f-imine. This, in turn, reverses the direction of intramolecular charge transfer (ICT). The imine reversal is further manifested in the orbital overlap of the Re and bpy in the metalated COFs, significantly affecting the excited state and charge separation pathway. The excited state was more prolonged in the Re-f-COF than in the Re-r-COF. These differences brought about by slight structural changes had a huge impact on the overall catalytic performance, making the isomeric Re-f-COF a better photocatalyst over the Re-r-COF.

The choice of building units can influence the local electron density and charge separation, determining the catalytic efficiency. High local electron density can be obtained using building units with electron-rich and electron-deficient properties (ERP and EDP) linked through an efficient charge transfer channel. Keeping this in perspective, VL-MCOF-1 was designed by Knoevenagel condensation of the electron-rich metal cluster $\text{Cu}_3(\text{PyCA})_3$ ED 3,5-dicyano-2,4,6-trimethylpyridine (DCTMP) linked *via* robust $-\text{C}=\text{C}-$ linkage.¹³⁶ As expected, VL-MCOF-1 with a well-defined molecular junction showed a high CO_2 to HCOOH reduction efficiency of $283.41 \mu\text{mol g}^{-1} \text{h}^{-1}$ with 97.1% selectivity. However, replacing any one of the strong ED or ER with weaker moieties led to much inferior photocatalytic performance. For instance, VL-MCOF-2 bearing the same metal cluster and linkage but a weaker ED, 2,4,6-trimethyl-1,3,5-triazine, gave a HCOOH generation rate of $195.57 \mu\text{mol g}^{-1} \text{h}^{-1}$ with 96.34% selectivity, and the $\text{g-C}_{34}\text{N}_6$ -COF, formed with a weak ER and a strong ED DCTMP, gave a much lower HCOOH production of $31.53 \mu\text{mol g}^{-1} \text{h}^{-1}$ with 82.09% selectivity. Light utilization was significantly enhanced in VL-MCOF-1 due to the synergistic effect of ER and ED groups and the appropriate CTC, highlighting the importance of modulating local electron density in the overall catalytic performance.

8. Conclusions and future outlook

The molecular engineering of COFs with structural and functional modulation to boost the photocatalytic CO_2 reduction efficiency is currently emerging as a promising avenue. In this review, we have summarized the key developments in this field and tried to evaluate the key parameters instrumental for improving the catalytic properties. We have classified COF-based photocatalysts into metalated and metal-free categories and provided an in-depth analysis of the various synthetic protocols developed in these areas. Our discussion encompasses COFs with intrinsic single-atom metallic active sites as well as those functionalized through post-synthetic modifications. Additionally, we have highlighted significant systems designed to leverage the nanoconfinement effects of COF pores. Key design strategies for developing metal-free photocatalysts have also been thoroughly examined. Throughout the discussion, we have emphasized the strategies researchers have employed to address the challenges associated with photocatalytic CO_2 reduction using covalent organic framework photocatalysts.

The development of futuristic catalytic systems requires taking the pros and cons of the process into account simultaneously. While high efficiency and selectivity have been obtained with COFs, the rampant use of sacrificial agents like TEOA and organic solvents is a cause of concern. On the one hand, incorporating these additives renders the process economically unsustainable; more critically, their degradation under reaction conditions could lead to overestimating the product, hindering future advancements. Efforts need to be made to increase the sustainability of the process by developing efficient catalysts that can perform in the water medium. Design strategies must be developed to increase the local concentration of CO_2 , promote the challenging 4e^- water oxidation process, and minimize the competitive hydrogen evolution reaction in an aqueous medium.

Another organic photocatalyst, such as graphitic carbon nitride ($\text{g-C}_3\text{N}_4$), can undergo rapid self-decomposition under reaction conditions, contributing to gaseous byproducts that might be misinterpreted as CO_2 reduction products. Therefore, comprehensive isotopic studies are crucial to eliminate such ambiguities. Furthermore, understanding the catalytic mechanism in COF-based catalysts remains challenging due to their heterogeneous nature. However, with advancements in the field, detailed *in situ* mechanistic investigations are essential to elucidate the reaction pathways and identify the intermediates involved. Although COFs are stable for several cycles, consistent efforts are required to improve their photostability under harsh conditions.

COFs are predominantly synthesized as insoluble powdered materials, subsequently dispersed and utilized for catalysis. However, for practical applications, it is essential to control the macroscopic architecture of COFs, where alternative forms such as films, membranes, and granules could offer greater viability. While the chemical tunability of COFs has been extensively explored, studies on their nanomorphologies and their influence on bulk-scale properties remain limited. Moreover, nanomorphologies significantly affect catalytic performance; for example, COF nanosheets, with their higher density of exposed active sites compared to bulk COFs, facilitate faster diffusion kinetics and enhanced catalytic efficiency. Despite notable progress in improving COF processability, further efforts are needed to advance this area. A comprehensive understanding of the morphology–structure–function interplay is crucial for optimizing their practical applications. The large-scale synthesis of COFs and their cost also need to be considered.

The ability to fine-tune the molecular structure underscores the potential of reticular chemistry to play a pivotal role in designing next-generation CO_2 reduction systems. However, the field is still in its infancy, and unlocking its full potential necessitates significant effort to open new avenues toward practical solutions for photocatalytic CO_2 reduction.

Author contributions

Shibani Mohata: conceptualization, writing – original draft, writing – reviewing and editing; Poulam Majumder: global



checking; and Rahul Banerjee: conceptualization, writing – reviewing and editing.

Data availability

No primary research results, software or code have been included and no new data were generated or analysed as part of this review.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

S. M. and P. M. acknowledge the IISER-Kolkata IPhD program for fellowship support. R. B. acknowledges the funding from the DST Project; DST/C3E/MI2.0/CCUS/2K23/CALL/2023/153, submitted against FOA R&D in the area of CCUS with Mission Innovation and ANRF SUPRA [SPR/2021/000020] for funding.

References

- W. Gao, S. Liang, R. Wang, Q. Jiang, Y. Zhang, Q. Zheng, B. Xie, C. Y. Toe, X. Zhu, J. Wang, L. Huang, Y. Gao, Z. Wang, C. Jo, Q. Wang, L. Wang, Y. Liu, B. Louis, J. Scott, A.-C. Roger, R. Amal, H. He and S.-E. Park, *Chem. Soc. Rev.*, 2020, **49**, 8584–8686.
- C. Hepburn, E. Adlen, J. Beddington, E. A. Carter, S. Fuss, N. Mac Dowell, J. C. Minx, P. Smith and C. K. Williams, *Nature*, 2019, **575**, 87–97.
- S. Navarro-Jaén, M. Virginie, J. Bonin, M. Robert, R. Wojcieszak and A. Y. Khodakov, *Nat. Rev. Chem.*, 2021, **5**, 564–579.
- S. Zhang, Q. Fan, R. Xia and T. J. Meyer, *Acc. Chem. Res.*, 2020, **53**, 255–264.
- Q.-J. Wu, J. Liang, Y.-B. Huang and R. Cao, *Acc. Chem. Res.*, 2022, **55**, 2978–2997.
- S. Bierbaumer, M. Nattermann, L. Schulz, R. Zschoche, T. J. Erb, C. K. Winkler, M. Tinzl and S. M. Glueck, *Chem. Rev.*, 2023, **123**, 5702–5754.
- S. Roy, A. Cherevotan and S. C. Peter, *ACS Energy Lett.*, 2018, **3**, 1938–1966.
- S. Nitopi, E. Bertheussen, S. B. Scott, X. Liu, A. K. Engstfeld, S. Horch, B. Seger, I. E. L. Stephens, K. Chan, C. Hahn, J. K. Nørskov, T. F. Jaramillo and I. Chorkendorff, *Chem. Rev.*, 2019, **119**, 7610–7672.
- B. Chang, H. Pang, F. Raziq, S. Wang, K.-W. Huang, J. Ye and H. Zhang, *Energy Environ. Sci.*, 2023, **16**, 4714–4758.
- S. Fang, M. Rahaman, J. Bharti, E. Reisner, M. Robert, G. A. Ozin and Y. H. Hu, *Nat. Rev. Methods Primers*, 2023, **3**, 61.
- W. Gao, H. Li, J. Hu, Y. Yang, Y. Xiong, J. Ye, Z. Zou and Y. Zhou, *Chem. Sci.*, 2024, **15**, 14081–14103.
- L. Yang, Z. Chen, Q. Cao, H. Liao, J. Gao, L. Zhang, W. Wei, H. Li and J. Lu, *Adv. Mater.*, 2024, **36**, 2306758.
- P. Zhou, M. Luo and S. Guo, *Nat. Rev. Chem.*, 2022, **6**, 823–838.
- S. Das, P. Heasman, T. Ben and S. Qiu, *Chem. Rev.*, 2017, **117**, 1515–1563.
- B. Mishra, A. Alam, A. Chakraborty, B. Kumbhakar, S. Ghosh, P. Pachfule and A. Thomas, *Adv. Mater.*, 2024, 2413118.
- A. Basak, S. Karak and R. Banerjee, *J. Am. Chem. Soc.*, 2023, **145**, 7592–7599.
- A. Rodríguez-Camargo, K. Endo and B. V. Lotsch, *Angew. Chem., Int. Ed.*, 2024, **63**, e202413096.
- Q. Lin, Y. Yusran, J. Xing, Y. Li, J. Zhang, T. Su, L. Yang, J. Suo, L. Zhang, Q. Li, H. Wang, Q. Fang, Z.-T. Li and D.-W. Zhang, *ACS Appl. Mater. Interfaces*, 2024, **16**, 5869–5880.
- G.-F. Liu, Z.-W. Li, Z.-J. Huang, Z. Zhou, Y.-X. Li, A. Huang, Z. Cai, G. Ouyang, B.-H. Ye and Y.-B. Zhang, *J. Am. Chem. Soc.*, 2025, **147**, 1840–1850.
- C. S. Diercks, Y. Liu, K. E. Cordova and O. M. Yaghi, *Nat. Mater.*, 2018, **17**, 301–307.
- M. Kim, J. Yi, S.-H. Park and S. S. Park, *Adv. Mater.*, 2023, **35**, 2203791.
- N. Keller and T. Bein, *Chem. Soc. Rev.*, 2021, **50**, 1813–1845.
- Z. Chen, J. Wang, M. Hao, Y. Xie, X. Liu, H. Yang, G. I. N. Waterhouse, X. Wang and S. Ma, *Nat. Commun.*, 2023, **14**, 1106.
- S. Bag, H. S. Sasmal, S. P. Chaudhary, K. Dey, D. Blätte, R. Guntermann, Y. Zhang, M. Položij, A. Kuc, A. Shelke, R. K. Vijayaraghavan, T. G. Ajithkumar, S. Bhattacharyya, T. Heine, T. Bein and R. Banerjee, *J. Am. Chem. Soc.*, 2023, **145**, 1649–1659.
- A. Dhakshinamoorthy, S. Navalon, A. Corma and H. Garcia, *Energy Environ. Sci.*, 2012, **5**, 9217–9233.
- J. Di, C. Chen, S.-Z. Yang, S. Chen, M. Duan, J. Xiong, C. Zhu, R. Long, W. Hao, Z. Chi, H. Chen, Y.-X. Weng, J. Xia, L. Song, S. Li, H. Li and Z. Liu, *Nat. Commun.*, 2019, **10**, 2840.
- J. Xie, R. Jin, A. Li, Y. Bi, Q. Ruan, Y. Deng, Y. Zhang, S. Yao, G. Sankar, D. Ma and J. Tang, *Nat. Catal.*, 2018, **1**, 889–896.
- O. Stroyuk, A. Raevskaya and N. Gaponik, *Chem. Soc. Rev.*, 2018, **47**, 5354–5422.
- H. Mai, D. Chen, Y. Tachibana, H. Suzuki, R. Abe and R. A. Caruso, *Chem. Soc. Rev.*, 2021, **50**, 13692–13729.
- J. Twilton, C. Le, P. Zhang, M. H. Shaw, R. W. Evans and D. W. C. MacMillan, *Nat. Rev. Chem.*, 2017, **1**, 0052.
- C. D. Windle and R. N. Perutz, *Coord. Chem. Rev.*, 2012, **256**, 2562–2570.
- C. Costentin and J.-M. Savéant, *Nat. Rev. Chem.*, 2017, **1**, 0087.
- H. Kumagai, Y. Tamaki and O. Ishitani, *Acc. Chem. Res.*, 2022, **55**, 978–990.
- K. Li, B. Peng and T. Peng, *ACS Catal.*, 2016, **6**, 7485–7527.
- H. Xiong, Y. Dong, D. Liu, R. Long, T. Kong and Y. Xiong, *J. Phys. Chem. Lett.*, 2022, **13**, 1272–1282.
- D. Li, M. Kassymova, X. Cai, S.-Q. Zang and H.-L. Jiang, *Coord. Chem. Rev.*, 2020, **412**, 213262.



37 A. G. Slater and A. I. Cooper, *Science*, 2015, **348**, aaa8075.

38 T. D. Bennett, F.-X. Coudert, S. L. James and A. I. Cooper, *Nat. Mater.*, 2021, **20**, 1179–1187.

39 J. D. Wuest, *Nat. Commun.*, 2020, **11**, 4652.

40 A. Giri, Y. Khakre, G. Shreeraj, T. K. Dutta, S. Kundu and A. Patra, *J. Mater. Chem. A*, 2022, **10**, 17077–17121.

41 S. Navalón, A. Dhakshinamoorthy, M. Álvaro, B. Ferrer and H. García, *Chem. Rev.*, 2023, **123**, 445–490.

42 J.-D. Xiao and H.-L. Jiang, *Acc. Chem. Res.*, 2019, **52**, 356–366.

43 T. Banerjee, F. Podjaski, J. Kröger, B. P. Biswal and B. V. Lotsch, *Nat. Rev. Mater.*, 2021, **6**, 168–190.

44 T.-X. Wang, H.-P. Liang, D. A. Anito, X. Ding and B.-H. Han, *J. Mater. Chem. A*, 2020, **8**, 7003–7034.

45 J. Y. Choi, B. Check, X. Fang, S. Blum, H. T. B. Pham, K. Tayman and J. Park, *J. Am. Chem. Soc.*, 2024, **146**, 11319–11327.

46 Z. Meng and K. A. Mirica, *Chem. Soc. Rev.*, 2021, **50**, 13498–13558.

47 N.-N. Vu, S. Kaliaguine and T.-O. Do, *Adv. Funct. Mater.*, 2019, **29**, 1901825.

48 Y. Kuramochi, O. Ishitani and H. Ishida, *Coord. Chem. Rev.*, 2018, **373**, 333–356.

49 X. Chang, T. Wang and J. Gong, *Energy Environ. Sci.*, 2016, **9**, 2177–2196.

50 J. Yang, Z. Chen, L. Zhang and Q. Zhang, *ACS Nano*, 2024, **18**, 21804–21835.

51 X. Li, Y. Sun, J. Xu, Y. Shao, J. Wu, X. Xu, Y. Pan, H. Ju, J. Zhu and Y. Xie, *Nat. Energy*, 2019, **4**, 690–699.

52 J. Albero, Y. Peng and H. García, *ACS Catal.*, 2020, **10**, 5734–5749.

53 G. M. Tomboc, S. Choi, T. Kwon, Y. J. Hwang and K. Lee, *Adv. Mater.*, 2020, **32**, 1908398.

54 Ž. Kovacić, B. Likozar and M. Huš, *ACS Catal.*, 2020, **10**, 14984–15007.

55 N.-Y. Huang, J.-Q. Shen, X.-W. Zhang, P.-Q. Liao, J.-P. Zhang and X.-M. Chen, *J. Am. Chem. Soc.*, 2022, **144**, 8676–8682.

56 J. Li, G. Chen, Y. Zhu, Z. Liang, A. Pei, C.-L. Wu, H. Wang, H. R. Lee, K. Liu, S. Chu and Y. Cui, *Nat. Catal.*, 2018, **1**, 592–600.

57 Y. Tamaki and O. Ishitani, *ACS Catal.*, 2017, **7**, 3394–3409.

58 H. Shen, T. Peppel, J. Strunk and Z. Sun, *Sol. RRL*, 2020, **4**, 1900546.

59 W. Xie, J. Xu, U. Md Idros, J. Katsuhira, M. Fukui, M. Hayashi, M. Yamanaka, Y. Kobori and R. Matsubara, *Nat. Chem.*, 2023, **15**, 794–802.

60 Q. Guo, F. Liang, X.-B. Li, Y.-J. Gao, M.-Y. Huang, Y. Wang, S.-G. Xia, X.-Y. Gao, Q.-C. Gan, Z.-S. Lin, C.-H. Tung and L.-Z. Wu, *Chem*, 2019, **5**, 2605–2616.

61 R. Das, S. Chakraborty and S. C. Peter, *ACS Energy Lett.*, 2021, **6**, 3270–3274.

62 R. N. Sampaio, D. C. Grills, D. E. Polyansky, D. J. Szalda and E. Fujita, *J. Am. Chem. Soc.*, 2020, **142**, 2413–2428.

63 Z. Liu, J. Li, Z. Chen, M. Li, L. Wang, S. Wu and J. Zhang, *Appl. Catal., B*, 2023, **326**, 122338.

64 P. Chen, X. a Dong, M. Huang, K. Li, L. Xiao, J. Sheng, S. Chen, Y. Zhou and F. Dong, *ACS Catal.*, 2022, **12**, 4560–4570.

65 O. M. Yaghi, M. J. Kalmutzki and C. S. Diercks, *Introduction to Reticular Chemistry*, 2019, pp. 267–283, DOI: [10.1002/9783527821099.ch11](https://doi.org/10.1002/9783527821099.ch11).

66 S. Kandambeth, K. Dey and R. Banerjee, *J. Am. Chem. Soc.*, 2019, **141**, 1807–1822.

67 B. B. Rath, S. Krause and B. V. Lotsch, *Adv. Funct. Mater.*, 2024, **34**, 2309060.

68 J. Guo and D. Jiang, *ACS Cent. Sci.*, 2020, **6**, 869–879.

69 H. S. Sasmal, A. Kumar Mahato, P. Majumder and R. Banerjee, *J. Am. Chem. Soc.*, 2022, **144**, 11482–11498.

70 K. Dey, S. Mohata and R. Banerjee, *ACS Nano*, 2021, **15**, 12723–12740.

71 J. Yang, X. Zhang, W. Si, Y. Cao, J. Qian, Y. Li, B. Li and W. Qin, *ACS Catal.*, 2024, **14**, 2022–2030.

72 S. Mohata, K. Dey, S. Bhunia, N. Thomas, E. B. Gowd, T. G. Ajithkumar, C. M. Reddy and R. Banerjee, *J. Am. Chem. Soc.*, 2022, **144**, 400–409.

73 D. Rodríguez-San-Miguel, C. Montoro and F. Zamora, *Chem. Soc. Rev.*, 2020, **49**, 2291–2302.

74 C.-H. Hsueh, C. He, J. Zhang, X. Tan, H. Zhu, W.-C. M. Cheong, A.-Z. Li, X. Chen, H. Duan, Y. Zhao and C. Chen, *J. Am. Chem. Soc.*, 2024, **146**, 33857–33864.

75 X. Kang, X. Wu, X. Han, C. Yuan, Y. Liu and Y. Cui, *Chem. Sci.*, 2020, **11**, 1494–1502.

76 F. Haase and B. V. Lotsch, *Chem. Soc. Rev.*, 2020, **49**, 8469–8500.

77 K. Koner, S. Mohata, Y. Ogaeri, Y. Nishiyama, M. A. Addicoat and R. Banerjee, *Angew. Chem., Int. Ed.*, 2024, **63**, e202316873.

78 E. Jin, M. Asada, Q. Xu, S. Dalapati, M. A. Addicoat, M. A. Brady, H. Xu, T. Nakamura, T. Heine, Q. Chen and D. Jiang, *Science*, 2017, **357**, 673–676.

79 S. Xu, M. Richter and X. Feng, *Acc. Mater. Res.*, 2021, **2**, 252–265.

80 Y.-N. Gong, X. Guan and H.-L. Jiang, *Coord. Chem. Rev.*, 2023, **475**, 214889.

81 R. Wang, Y. Yuan, K.-T. Bang and Y. Kim, *ACS Mater. Au*, 2023, **3**, 28–36.

82 L. Yao, A. M. Pütz, H. Vignolo-González and B. V. Lotsch, *J. Am. Chem. Soc.*, 2024, **146**, 9479–9492.

83 P. M. Stanley, J. Haimerl, N. B. Shustova, R. A. Fischer and J. Warnan, *Nat. Chem.*, 2022, **14**, 1342–1356.

84 S. Mohata, R. Das, K. Koner, M. Riyaz, K. Das, S. Chakraborty, Y. Ogaeri, Y. Nishiyama, S. C. Peter and R. Banerjee, *J. Am. Chem. Soc.*, 2023, **145**, 23802–23813.

85 D. A. Cagan, D. Bím, N. P. Kazmierczak and R. G. Hadt, *ACS Catal.*, 2024, **14**, 9055–9076.

86 S. Yang, W. Hu, X. Zhang, P. He, B. Pattengale, C. Liu, M. Cendejas, I. Hermans, X. Zhang, J. Zhang and J. Huang, *J. Am. Chem. Soc.*, 2018, **140**, 14614–14618.

87 Z. Fu, X. Wang, A. M. Gardner, X. Wang, S. Y. Chong, G. Neri, A. J. Cowan, L. Liu, X. Li, A. Vogel, R. Clowes, M. Bilton, L. Chen, R. S. Sprick and A. I. Cooper, *Chem. Sci.*, 2020, **11**, 543–550.



88 Y.-Z. Cheng, W. Ji, P.-Y. Hao, X.-H. Qi, X. Wu, X.-M. Dou, X.-Y. Bian, D. Jiang, F.-T. Li, X.-F. Liu, D.-H. Yang, X. Ding and B.-H. Han, *Angew. Chem., Int. Ed.*, 2023, **62**, e202308523.

89 W. Zhong, R. Sa, L. Li, Y. He, L. Li, J. Bi, Z. Zhuang, Y. Yu and Z. Zou, *J. Am. Chem. Soc.*, 2019, **141**, 7615–7621.

90 Q. Zhang, S. Gao, Y. Guo, H. Wang, J. Wei, X. Su, H. Zhang, Z. Liu and J. Wang, *Nat. Commun.*, 2023, **14**, 1147.

91 E. Nikoloudakis, I. López-Duarte, G. Charalambidis, K. Ladomenou, M. Ince and A. G. Coutsolelos, *Chem. Soc. Rev.*, 2022, **51**, 6965–7045.

92 M. Lu, J. Liu, Q. Li, M. Zhang, M. Liu, J.-L. Wang, D.-Q. Yuan and Y.-Q. Lan, *Angew. Chem., Int. Ed.*, 2019, **58**, 12392–12397.

93 Y. H. Kim, J.-P. Jeon, Y. Kim, H.-J. Noh, J.-M. Seo, J. Kim, G. Lee and J.-B. Baek, *Angew. Chem., Int. Ed.*, 2023, **62**, e202307991.

94 T.-X. Luan, J.-R. Wang, K. Li, H. Li, F. Nan, W. W. Yu and P.-Z. Li, *Small*, 2023, **19**, 2303324.

95 L. Ran, Z. Li, B. Ran, J. Cao, Y. Zhao, T. Shao, Y. Song, M. K. H. Leung, L. Sun and J. Hou, *J. Am. Chem. Soc.*, 2022, **144**, 17097–17109.

96 Y. Yang, H.-Y. Zhang, Y. Wang, L.-H. Shao, L. Fang, H. Dong, M. Lu, L.-Z. Dong, Y.-Q. Lan and F.-M. Zhang, *Adv. Mater.*, 2023, **35**, 2304170.

97 W. Zhou, X. Wang, W. Zhao, N. Lu, D. Cong, Z. Li, P. Han, G. Ren, L. Sun, C. Liu and W.-Q. Deng, *Nat. Commun.*, 2023, **14**, 6971.

98 Y. Yang, Y. Lu, H.-Y. Zhang, Y. Wang, H.-L. Tang, X.-J. Sun, G. Zhang and F.-M. Zhang, *ACS Sustainable Chem. Eng.*, 2021, **9**, 13376–13384.

99 J. Zhou, J. Li, L. Kan, L. Zhang, Q. Huang, Y. Yan, Y. Chen, J. Liu, S.-L. Li and Y.-Q. Lan, *Nat. Commun.*, 2022, **13**, 4681.

100 X. Wang, X. Ding, Y. Jin, D. Qi, H. Wang, Y. Han, T. Wang and J. Jiang, *Angew. Chem., Int. Ed.*, 2023, **62**, e202302808.

101 S. Li, C. Gao, H. Yu, Y. Wang, S. Wang, W. Ding, L. Zhang and J. Yu, *Angew. Chem., Int. Ed.*, 2024, **63**, e202409925.

102 M. Lu, Q. Li, J. Liu, F.-M. Zhang, L. Zhang, J.-L. Wang, Z.-H. Kang and Y.-Q. Lan, *Appl. Catal., B*, 2019, **254**, 624–633.

103 J. Wang, W. Zhu, F. Meng, G. Bai, Q. Zhang and X. Lan, *ACS Catal.*, 2023, **13**, 4316–4329.

104 X. Lan, H. Li, Y. Liu, Y. Zhang, T. Zhang and Y. Chen, *Angew. Chem., Int. Ed.*, 2024, **63**, e202407092.

105 L. Liu and A. Corma, *Nat. Rev. Mater.*, 2021, **6**, 244–263.

106 P. Majumder, S. Mohata, H. S. Sasmal, B. Chandra, H. Kuiry and R. Banerjee, *Angew. Chem., Int. Ed.*, 2024, **63**, e202412122.

107 S.-S. Wang and G.-Y. Yang, *Chem. Rev.*, 2015, **115**, 4893–4962.

108 M. Lu, M. Zhang, J. Liu, T. Y. Yu, J. N. Chang, L. J. Shang, S. L. Li and Y. Q. Lan, *J. Am. Chem. Soc.*, 2022, **144**, 1861–1871.

109 H. Zhong, R. Sa, H. Lv, S. Yang, D. Yuan, X. Wang and R. Wang, *Adv. Funct. Mater.*, 2020, **30**, 2002654.

110 H. Li, C. Cheng, Z. Yang and J. Wei, *Nat. Commun.*, 2022, **13**, 6466.

111 M. Zhang, M. Lu, Z.-L. Lang, J. Liu, M. Liu, J.-N. Chang, L.-Y. Li, L.-J. Shang, M. Wang, S.-L. Li and Y.-Q. Lan, *Angew. Chem., Int. Ed.*, 2020, **59**, 6500–6506.

112 Y. Qiu, C. Jiang, X. Xin, Y.-Y. Li, H. Wang, J. Xu, H. Lin, L. Wang and V. Turkevich, *ACS Appl. Nano Mater.*, 2024, **7**, 11234–11247.

113 M. Xu, C. Lai, X. Liu, B. Li, M. Zhang, F. Xu, S. Liu, L. Li, L. Qin, H. Yi and Y. Fu, *J. Mater. Chem. A*, 2021, **9**, 24148–24174.

114 L. Zou, R. Sa, H. Zhong, H. Lv, X. Wang and R. Wang, *ACS Catal.*, 2022, **12**, 3550–3557.

115 K. Guo, X. Zhu, L. Peng, Y. Fu, R. Ma, X. Lu, F. Zhang, W. Zhu and M. Fan, *Chem. Eng. J.*, 2021, **405**, 127011.

116 X. An, J. Bian, K. Zhu, R. Liu, H. Liu and J. Qu, *Chem. Eng. J.*, 2022, **442**, 135279.

117 X. Yu, Z. Yang, B. Qiu, S. Guo, P. Yang, B. Yu, H. Zhang, Y. Zhao, X. Yang, B. Han and Z. Liu, *Angew. Chem., Int. Ed.*, 2019, **58**, 632–636.

118 S. Wang, X. Hai, X. Ding, S. Jin, Y. Xiang, P. Wang, B. Jiang, F. Ichihara, M. Oshikiri, X. Meng, Y. Li, W. Matsuda, J. Ma, S. Seki, X. Wang, H. Huang, Y. Wada, H. Chen and J. Ye, *Nat. Commun.*, 2020, **11**, 1149.

119 O. P. Dimitriev, *Chem. Rev.*, 2022, **122**, 8487–8593.

120 K. Lei, D. Wang, L. Ye, M. Kou, Y. Deng, Z. Ma, L. Wang and Y. Kong, *ChemSusChem*, 2020, **13**, 1725–1729.

121 Z. Shan, M. Wu, D. Zhu, X. Wu, K. Zhang, R. Verduzco and G. Zhang, *J. Am. Chem. Soc.*, 2022, **144**, 5728–5733.

122 S. Gao, Q. Zhang, X. Su, X. Wu, X.-G. Zhang, Y. Guo, Z. Li, J. Wei, H. Wang, S. Zhang and J. Wang, *J. Am. Chem. Soc.*, 2023, **145**, 9520–9529.

123 J.-X. Cui, L.-J. Wang, L. Feng, B. Meng, Z.-Y. Zhou, Z.-M. Su, K. Wang and S. Liu, *J. Mater. Chem. A*, 2021, **9**, 24895–24902.

124 L.-J. Wang, R.-J. Wang, X. Zhang, J.-I. Mu, Z.-Y. Zhou and Z.-M. Su, *ChemSusChem*, 2020, **13**, 2973–2980.

125 S. Biswas, F. A. Rahimi, R. K. Saravanan, A. Dey, J. Chauhan, D. Surendran, S. Nath and T. K. Maji, *Chem. Sci.*, 2024, **15**, 16259–16270.

126 X. Yu, K. Gong, S. Tian, G. Gao, J. Xie and X.-H. Jin, *J. Mater. Chem. A*, 2023, **11**, 5627–5635.

127 J. Ren, C. Ji, B. Du, Q. Liu, K. Yu, D. Ahn, Z. Zhang, Y. Ye, C. R. Göb and D. Zhao, *J. Am. Chem. Soc.*, 2024, **146**, 30784–30789.

128 K. Sun, Y. Huang, Q. Wang, W. Zhao, X. Zheng, J. Jiang and H.-L. Jiang, *J. Am. Chem. Soc.*, 2024, **146**, 3241–3249.

129 J. Ding, X. Guan, J. Lv, X. Chen, Y. Zhang, H. Li, D. Zhang, S. Qiu, H.-L. Jiang and Q. Fang, *J. Am. Chem. Soc.*, 2023, **145**, 3248–3254.

130 L. Zou, Z.-A. Chen, D.-H. Si, S.-L. Yang, W.-Q. Gao, K. Wang, Y.-B. Huang and R. Cao, *Angew. Chem., Int. Ed.*, 2023, **62**, e202309820.

131 X. Wang, X. Ding, T. Wang, K. Wang, Y. Jin, Y. Han, P. Zhang, N. Li, H. Wang and J. Jiang, *ACS Appl. Mater. Interfaces*, 2022, **14**, 41122–41130.

132 W. Liu, X. Li, C. Wang, H. Pan, W. Liu, K. Wang, Q. Zeng, R. Wang and J. Jiang, *J. Am. Chem. Soc.*, 2019, **141**, 17431–17440.



133 X. Wang, Z. Fu, L. Zheng, C. Zhao, X. Wang, S. Y. Chong, F. McBride, R. Raval, M. Bilton, L. Liu, X. Wu, L. Chen, R. S. Sprick and A. I. Cooper, *Chem. Mater.*, 2020, **32**, 9107–9114.

134 P. Dong, X. Xu, R. Luo, S. Yuan, J. Zhou and J. Lei, *J. Am. Chem. Soc.*, 2023, **145**, 15473–15481.

135 D. H. Streater, E. R. Kennehan, D. Wang, C. Fiankor, L. Chen, C. Yang, B. Li, D. Liu, F. Ibrahim, I. Hermans, K. L. Kohlstedt, L. Luo, J. Zhang and J. Huang, *J. Am. Chem. Soc.*, 2024, **146**, 4489–4499.

136 M. Zhang, P. Huang, J.-P. Liao, M.-Y. Yang, S.-B. Zhang, Y.-F. Liu, M. Lu, S.-L. Li, Y.-P. Cai and Y.-Q. Lan, *Angew. Chem., Int. Ed.*, 2023, **62**, e202311999.

