



 Cite this: *CrystEngComm*, 2015, 17, 7354

 Received 21st July 2015,  
 Accepted 19th August 2015

DOI: 10.1039/c5ce01430a

[www.rsc.org/crystengcomm](http://www.rsc.org/crystengcomm)

## Introduction

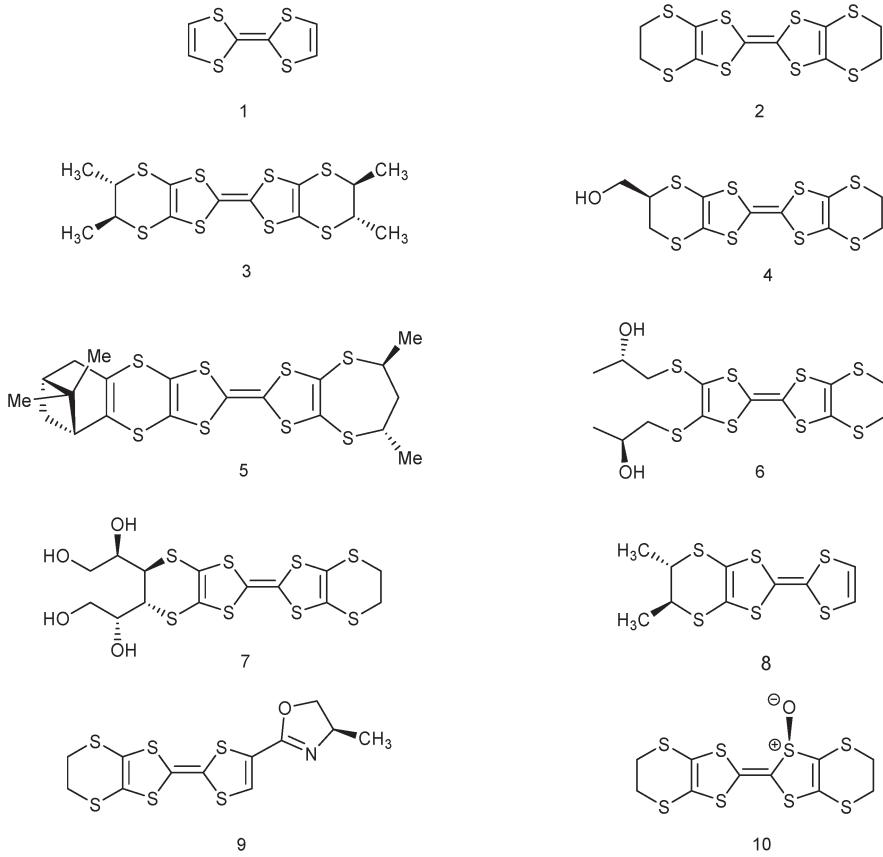
<sup>a</sup> School of Science and Technology, Nottingham Trent University, Clifton Lane, Nottingham NG11 8NS, UK. E-mail: lee.martin@ntu.ac.uk

<sup>b</sup> University College London, Department of Chemistry, 20 Gordon Street, London WC1H 0AJ, UK

<sup>c</sup> Department of Chemistry, University of Southampton, Highfield, Southampton, SO17 1BJ, UK





<sup>d</sup> School of Chemistry, Newcastle University, Newcastle upon Tyne, NE1 7RU, UK

<sup>†</sup> CCDC 1413630–1413635. For crystallographic data in CIF or other electronic format see DOI: 10.1039/c5ce01430a

The electrical properties of the radical cation salts of donors such as TTF **1** and BEDT-TTF **2** have attracted a lot of attention. Over 30 years ago Dunitz raised the question as to how the chirality of a material might affect its electrical properties, and prepared the enantiopure (*S,S,S,S*)-tetramethyl(BEDT-TTF) donor **3** and a family of its semiconducting radical cation salts.<sup>1</sup> In subsequent studies several series of salts from both enantiomers of **3** and its racemate were prepared. For the 2:1 salts with  $\text{AsF}_6^-$  or  $\text{SbF}_6^-$  the conductivities and activation energies were similar, while for the 1:1 salts with triiodide the racemate salt had lower conductivity and higher activation energy than the enantiomerically pure salts.<sup>2</sup> Very recently, this series of stereoisomers has been electrocrystallised with the tris(chloranilato)ferrate(III) ion to provide materials combining chirality, electrical conductivity and magnetic properties.<sup>3</sup> In addition donor **3** and a

also been introduced using a solvent *e.g.* (*S*)-*sec*-phenylethyl alcohol which is included in crystals of BEDT-TTF radical cation salts.<sup>20</sup> The various strategies for preparing chiral molecular conductors have been reviewed.<sup>21</sup>

We recently reported the preparation and crystal packing arrangements of four new chiral bis(pyrrolo)[3,4-*d*]tetraphiafulvalene derivatives **11–14** in which the two stereogenic centres carry a hydrogen, a methyl and either a phenyl or 1-naphthyl group, and the TTF is fused to pyrrole or pyrroline rings.<sup>22</sup> Most notable was that donors **11** and **12**, which have fully unsaturated heterocyclic systems, adopt crystal packings with  $4_3$  or near  $4_3$  chiral axes relating successive layers of donors. We now report the first radical cation salts obtained with these materials. Note that for **11** and **13** the stereogenic centres have the *S* configuration, and for **12** and **14** they have the *R* configuration.

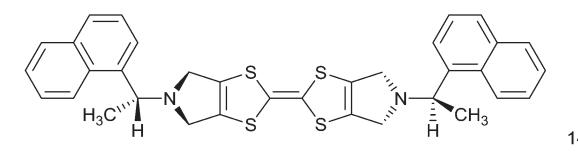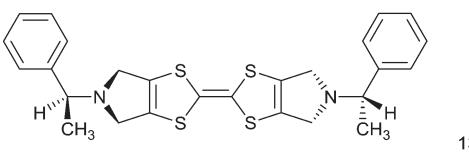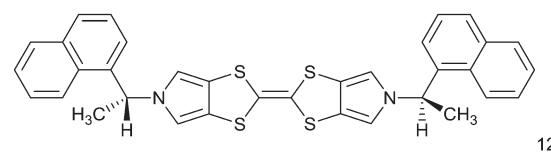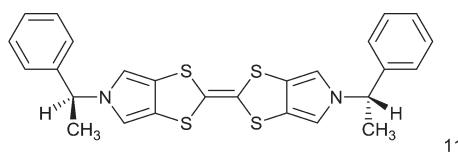

mixed metal oxalate network form a chiral ferromagnetic material.<sup>4</sup>

Rikken has shown that, for a chiral conducting material in a coaxial magnetic field, the size of the electrical resistance has a dependence on the handedness of the material, a property termed magnetochiral anisotropy, with measurements made on bismuth helices and carbon nanotubes.<sup>5</sup> To provide further materials for investigation we and others have prepared a range of enantiopure organosulfur donors, *e.g.* **4–10**<sup>6–12</sup> and have reported some of their radical cation salts.<sup>7,8,10,11</sup> In particular, Avarvari, Rikken *et al.* have shown that the metallic 2:1 salts of *R,R* or *S,S*-**8** with  $\text{ClO}_4^-$  crystallise in enantiomorphous hexagonal space groups and indeed show magnetochiral anisotropy.<sup>13</sup>

An alternative approach is to form salts of an achiral donor with a chiral anion, *e.g.* a tris(oxalate)metallate in (BEDT-TTF)<sub>4</sub>[(H<sub>3</sub>O)Cr(C<sub>2</sub>O<sub>4</sub>)<sub>3</sub>]<sub>2</sub>C<sub>6</sub>H<sub>5</sub>CN where one polymorph has the enantiomers partitioned into separate layers.<sup>14</sup> By using *R*-(-)-carvone as solvent, the first BEDT-TTF salts with a single enantiomer of the tris(oxalate)metallate have been obtained.<sup>15</sup> Further BEDT-TTF salts have been made with the enantiopure  $\text{Sb}_2(\text{l}-\text{tartrate})_2$  anion<sup>16</sup> as well as with racemic anions such as  $\text{SF}_5\text{CHFCF}_2\text{SO}_3^-$  and  $\text{Fe}(\text{III})(\text{croconate})_3$ , and the salt of enantiopure tetramethyl-BEDT-TTF with the racemic TRISPHAT anion has been prepared.<sup>17–19</sup> Chirality has

## Results and discussion

Cyclic voltammetry measurements demonstrated that all four donors showed two oxidation processes, with the pyrrolo-fused donors having slightly lower oxidation potentials than the dihydropyrrolo-fused systems (Table 1). Electrocrystallisations with tetrabutylammonium triiodide have produced crystalline salts from three of these donors whose structures have been determined by single-crystal X-ray crystallography: **11**·I<sub>3</sub> and **11**·I<sub>3</sub>·0.5THF; a series of three related salts from **12**, *viz.* **12**·I<sub>3</sub>·solvent (THF, chlorobenzene or DCM); and **13**·I<sub>3</sub> (Tables 2 and 3). These are the first radical cation salts reported from the bis(pyrrolo)TTF system, though this molecular unit has been incorporated in catenanes and rotaxanes in which the TTF system forms charge transfer interactions with species such as 4,4'-bipyridinium dications in *cyclo*-bis(paraquat-*p*-phenylene).<sup>23</sup> For salts of donors **11** and **12**, the cations show lengthening of the central double bond from 1.352–1.356 Å to *ca.* 1.40 Å, and shortening of the C–S bonds, especially those at the centre of the molecule (from 1.744–1.783 Å to *ca.* 1.73 Å), but only minor changes in the pyrrole rings.

The six triiodide salts are all of 1:1 stoichiometry but show a variety of packing modes, with inclusion of solvent in some cases, in which the triiodides are packed alongside the



**Table 1** Cyclic voltammetry data for donors<sup>a</sup>

| Donor | <i>E</i> <sub>1</sub> (V) | <i>E</i> <sub>2</sub> (V) |
|-------|---------------------------|---------------------------|
| 11    | 0.36                      | 0.86                      |
| 12    | 0.36                      | 0.86                      |
| 13    | 0.40                      | 0.90                      |
| 14    | 0.41                      | 0.88                      |

<sup>a</sup> Measured relative to Ag/AgCl at a platinum electrode in dichloromethane containing 0.1 M *n*-Bu<sub>4</sub>NPF<sub>6</sub> as charge carrier and using a 100 mV s<sup>-1</sup> scan.

donors either in head-to-tail pairs, or in continuous lines, or even in a castellated array. The donor cations are packed in face-to-face pairs. Incorporation of iodides parallel to the TTF unit has been observed in triiodide salts of TTF itself and its derivatives bearing two fused cyclopentene or cyclohexene rings,<sup>24</sup> as well as in bis(2-hydroxypropylthio)ethylenedithio-TTF.<sup>25</sup> The salts were found to be electrically insulating; data for salt 12-I<sub>3</sub>·THF could not be measured.

### Salts 11-I<sub>3</sub> and 11-I<sub>3</sub>·0.5THF

Two 1:1 triiodide salts of donor 11 have been characterized structurally: a triclinic phase grown as thin black diamonds

from dichloromethane, and an orthorhombic THF hemisolvate phase obtained as thin black needles. They both contain pairs of triiodide ions lying head-to-tail which lie side-by-side with pairs of donor cations which are oriented face-to-face. The bonding geometry at each pyrrole nitrogen atom is planar.

The asymmetric unit of the THF solvate phase contains two donor cations and two triiodide anions along with one THF molecule, which in the space group *P*2<sub>1</sub>2<sub>1</sub> gives eight cations, eight anions and four THF molecules per unit cell. Two important structural motifs can be identified: a pair of crystallographically independent donor cations packed face-to-face but with their TTF units offset in the direction of the longest molecular axis (Fig. 1), and a unit formed by two triiodides which are organized “head-to-tail” (I···I: 3.578(2) Å, with I–I···I angles 170.1 and 173.1°). These motifs are packed alternately along the *b* axis, and the 2<sub>1</sub> axis along *c* produces a herringbone pattern of these units in the *bc* plane (Fig. 2). Successive planes in the *a*-axis direction are related by the 2<sub>1</sub> axes along *a* (Fig. 2). The THF solvent molecules are surrounded principally by the chiral side chains of the donor cations. An alternative way of considering the packing arrangement is that the two structural motifs are packed into

**Table 2** Crystal data for triiodide salts

|   | 11-I <sub>3</sub> ·0.5THF   | 11-I <sub>3</sub>  | 12-I <sub>3</sub> ·THF   | 12-I <sub>3</sub> ·C <sub>6</sub> H <sub>5</sub> Cl   | 12-I <sub>3</sub> ·DCM   | 13-I <sub>3</sub>  |
|---|---|--|--|---|--|--|
| Formula   | C <sub>26</sub> H <sub>22</sub> N <sub>2</sub> S <sub>4</sub> I <sub>3</sub><br>·0.5C <sub>4</sub> H <sub>8</sub> O | C <sub>26</sub> H <sub>22</sub> N <sub>2</sub> S <sub>4</sub><br>·I <sub>3</sub> | C <sub>34</sub> H <sub>26</sub> N <sub>2</sub> S <sub>4</sub> I <sub>3</sub><br>·C <sub>4</sub> H <sub>8</sub> O | C <sub>34</sub> H <sub>26</sub> N <sub>2</sub> S <sub>4</sub> I <sub>3</sub><br>·C <sub>6</sub> H <sub>5</sub> Cl | C <sub>34</sub> H <sub>26</sub> N <sub>2</sub> S <sub>4</sub> I <sub>3</sub><br>·CH <sub>2</sub> Cl <sub>2</sub> | C <sub>26</sub> H <sub>26</sub> N <sub>2</sub> S <sub>4</sub> I <sub>3</sub> |
| <i>M</i> <sub>r</sub>   | 907.45  | 871.39   | 1043.66  | 1084.06   | 1056.43  | 875.43   |
| Crystal system  | Orthorhombic  | Triclinic  | Monoclinic   | Monoclinic  | Monoclinic   | Orthorhombic   |
| <i>a</i> (Å)  | 9.446(6)  | 9.4562(16)   | 25.5744(5)   | 26.3842(14)   | 25.618(4)  | 9.484(10)  |
| <i>b</i> (Å)  | 17.339(11)  | 9.5572(14)   | 8.9609(2)  | 9.0879(2)   | 8.9466(5)  | 19.551(14)   |
| <i>c</i> (Å)  | 37.04(2)  | 53.944(9)  | 19.6079(5)   | 19.4801(9)  | 19.623(2)  | 30.639(3)  |
| α (°)   | 90  | 89.206(5)  | 90   | 90  | 90   | 90   |
| β (°)   | 90  | 87.608(3)  | 123.5900(10)   | 123.371(7)  | 123.406(18)  | 90   |
| γ (°)   | 90  | 60.661(5)  | 90   | 90  | 90   | 90   |
| <i>V</i> (Å <sup>3</sup> )  | 6067(6)   | 4246.0(12)   | 3743.19(15)  | 3900.8(3)   | 3754.5(7)  | 5681(7)  |
| <i>Z</i>  | 8   | 6  | 4  | 4   | 4  | 8  |
| Space group   | <i>P</i> 2 <sub>1</sub> 2 <sub>1</sub> 2 <sub>1</sub>   | <i>P</i> 1   | <i>C</i> 2   | <i>C</i> 2  | <i>C</i> 2   | <i>P</i> 2 <sub>1</sub> 2 <sub>1</sub> 2 <sub>1</sub>                        |
| <i>T</i> (K)  | 120   | 120  | 120  | 120   | 120  | 120  |
| <i>D</i> <sub>c</sub> (g cm <sup>-3</sup> )   | 1.99  | 2.04   | 1.85   | 1.85  | 1.87   | 2.04   |
| λ (Å)   | 0.6893  | 0.71073  | 0.71073  | 0.71073   | 0.71073  | 0.71073  |
| μ (mm <sup>-1</sup> )   | 2.91  | 3.63   | 2.75   | 2.72  | 2.91   | 3.62   |
| No. of unique reflections   | 8693  | 19 478   | 8218   | 6467  | 6390   | 10 456   |
| No. of unique reflections with <i>F</i> > 4σ( <i>F</i> )                                      | 6035  | 10 434   | 7638   | 5804  | 5896   | 4940   |
| No. of refined parameters   | 682   | 1891   | 419  | 454   | 427  | 356  |
| Flack parameter   | 0.10(6)   | 0.12(3)  | 0.09(2)  | -0.02(2)  | 0.13(3)  | 0.12(6)  |
| <i>R</i> <sub>1</sub> , <i>wR</i> <sub>2</sub> for reflections with <i>F</i> > 4σ( <i>F</i> ) | 0.076, 0.161  | 0.084, 0.187   | 0.036, 0.081   | 0.028, 0.067  | 0.049, 0.133   | 0.159, 0.256   |

**Table 3** Conditions for preparation of radical cation salts

| Salt  | Solvent               | Current (μA) | Time (days) | Appearance of crystals |
|---|-----------------------|--------------|-------------|------------------------|
| 11-I <sub>3</sub> ·0.5THF                           | THF                   | 1.0          | 26          | Thin black needles     |
| 11-I <sub>3</sub>                                   | Dichloromethane       | 1.0          | 26          | Black diamond plates   |
| 12-I <sub>3</sub> ·THF                              | THF (20 ml)           | 0.5          | 28          | Black plates           |
| 12-I <sub>3</sub> ·C <sub>6</sub> H <sub>5</sub> Cl | Chlorobenzene         | 5.0          | 28          | Black plates           |
| 12-I <sub>3</sub> ·DCM                              | Dichloromethane       | 5.0          | 28          | Black plates           |
| 13-I <sub>3</sub>                                   | 1,1,1-Trichloroethane | 0.5          | 20          | Black plates           |



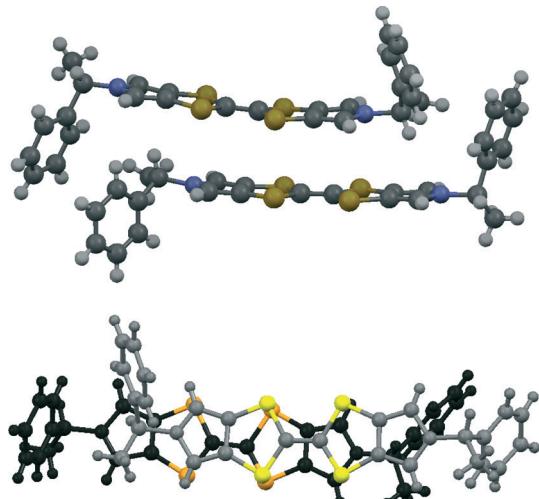


Fig. 1 Pair of donor cations in  $11\text{-I}_3\text{-}0.5\text{THF}$  showing their offset, face-to-face, with orientation viewed side on (above) and perpendicular to the heterocyclic system (below).

blocks extending half a unit cell length along the  $c$  axis, and the  $2_1$  axes along  $b$  and  $c$  produce the herringbone arrangement between successive blocks. The blocks interface *via* the phenylethyl sidechains of the donor cations and the THF molecules lie in this region.

Each  $(\text{I}_3^-)_2$  unit is surrounded by four donor cation pairs and *vice-versa*. Thus two cation pairs lie edge-on to the  $(\text{I}_3^-)_2$  unit, and two others present a donor face. The  $\text{I}\cdots\text{S}$  contacts are shorter to the edge-on donor cation pair with shortest contacts of 3.746(6) and 3.750(7) Å, while the shortest  $\text{I}\cdots\text{S}$  contacts to the faces of the other two donor cations are  $>4.1$  Å. There are also quite short  $\text{S}\cdots\text{S}$  contacts between the

adjacent donor cation pairs surrounding an  $(\text{I}_3^-)_2$  unit, notably 3.406(10), 3.412(10), 3.496(10) and 3.557(11) Å. The 1:1 salts of the enantiomers of tetramethyl-BEDT-TTF 3 with triiodide also contain head-to-tail pairs of triiodide,<sup>3</sup> a motif which has a similar length to the donor molecules.

The donor cation pairs lie with their bis(pyrrolo)TTF planes at 5.0° to each other, but slipped so that the central double bond for each donor overlaps with a dithiolo-pyrrole group of the other one (Fig. 1). One donor cation plane is perfectly planar and the other is slightly bowed. There are two very short  $\text{S}\cdots\text{S}$  contacts between these cations of 3.282(10) and 3.297(9) Å, which are *ca.* 0.6 Å shorter than the sum of two van der Waals radii for the asymmetrically shaped bonded S atom.<sup>26</sup> The conformations about the exocyclic N–C bonds at the ends of the donor cations are different. The phenyl group at one stereogenic centre and the hydrogen atom at the other are oriented roughly perpendicular to the heterocyclic plane and towards the other donor cation in the pair. The pair of donors fit together with the “perpendicular” phenyl group of each donor wrapping over the end of the other donor (Fig. 1).

The unsolvated triclinic phase in space group  $P\bar{1}$  is similar, but there are six independent donor cations, packed in three pairs, and three independent linear  $(\text{I}_3^-)_2$  units with  $\text{I}\cdots\text{I}$  separations of 3.498(3), 3.553(4) and 3.609(4) Å. A pair of donor cations is packed with a linear arrangement of two triiodide ions to form blocks perpendicular to the  $c$  axis (Fig. 3), similar to those in the orthorhombic phase. The difference is that in the triclinic phase there are three symmetry-unrelated blocks of this type sequentially along the  $c$  axis, which is over 50 Å long, with interfaces between the blocks formed by the phenylethyl sidechains (Fig. 3). In the orthorhombic phase there are just two, symmetry-related, blocks along the  $c$  axis. The modes of overlap between the members of the three independent pairs of donor cations are also similar to that in the orthorhombic phase, and within each pair there are two close  $\text{S}\cdots\text{S}$  contacts in the range

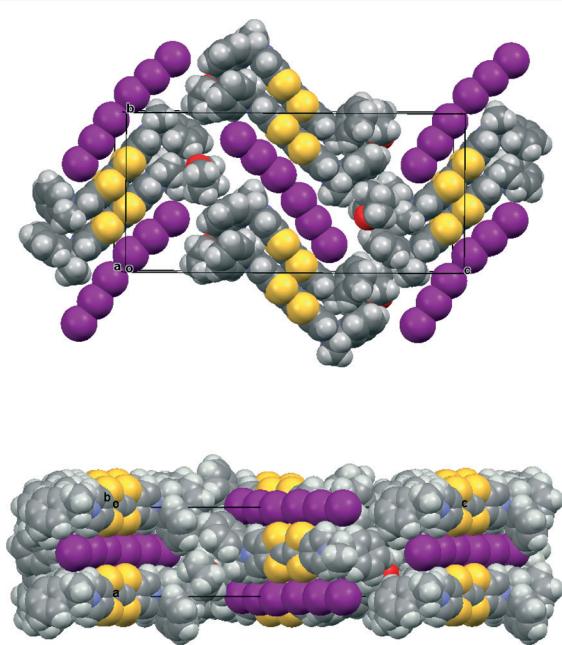


Fig. 2 Crystal packing of  $11\text{-I}_3\text{-}0.5\text{THF}$  viewed down the  $a$  axis (above) and down the  $b$  axis (below).

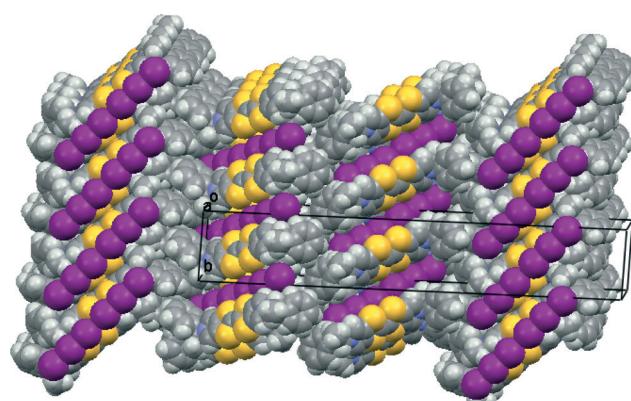


Fig. 3 Crystal packing of  $11\text{-I}_3$  showing one block of donor cation pairs and  $(\text{I}_3^-)_2$  units extending one third the way along the  $c$  axis and the arrangement of successive blocks along the  $c$  axis, viewed down the  $a$  axis.




**Table 4** Raman stretching frequencies for donors **11** and **13** and their triiodide salts


| Donor/salt                        | Raman frequencies (cm <sup>-1</sup> ) |
|-----------------------------------|---------------------------------------|
| <b>11</b>                         | 1485, 1549                            |
| <b>11</b> ·I <sub>3</sub>         | 1414, 1496                            |
| <b>11</b> ·I <sub>3</sub> ·0.5THF | 1412, 1492                            |
| <b>13</b>                         | 1471, 1538                            |
| <b>13</b> ·I <sub>3</sub>         | 1412, 1499                            |

3.341(14)–3.388(14) Å. Furthermore, there are S···S contacts between each set of donor cation pair neighbours surrounding each (I<sub>3</sub><sup>-</sup>)<sub>2</sub> unit in the range 3.503(13)–3.522(12) Å.

The state of oxidation of TTF and derived donors can be detected by observation of particular stretches in the Raman spectrum.<sup>27</sup> While donor **11** showed stretches at 1485 and 1549 cm<sup>-1</sup>, in the two salts of this donor, the corresponding stretches occurred at lower wavenumber, 1412–1414 and 1492–1496 cm<sup>-1</sup> (Table 4). These are the first measurements on the bis(pyrrolo)TTF system, but the results are reasonably consistent with a +1 oxidation state by comparison with results from TTF itself.

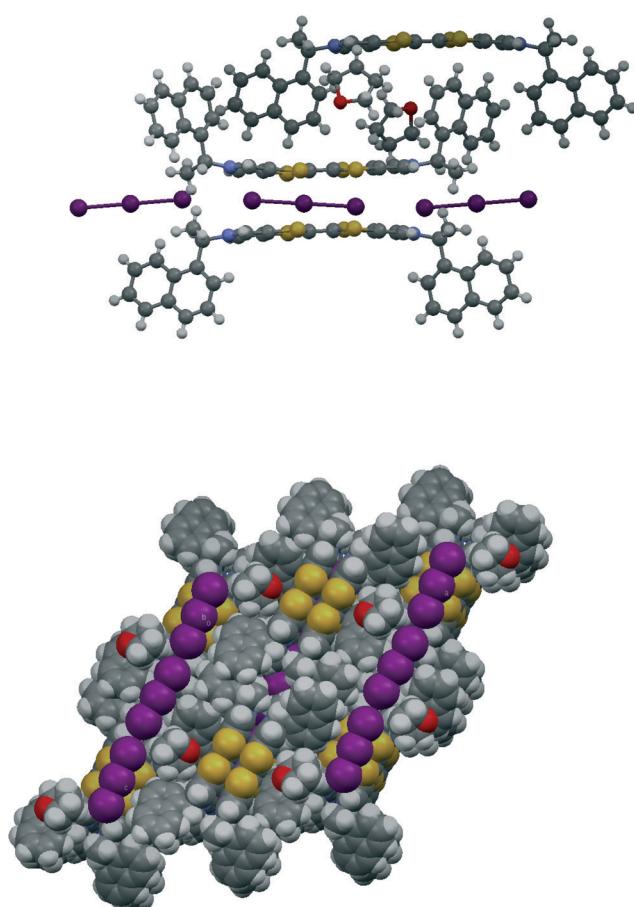

**Fig. 4** Section of crystal packing in **12**·I<sub>3</sub>·THF showing the conformation of the donor and the relative location of the lines of triiodides and the THF molecules (above), view of crystal packing looking down the *b* axis (below).

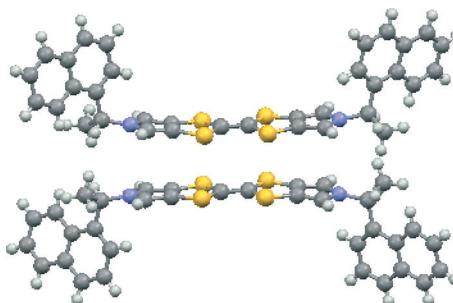


**Fig. 5** The donor pair in **12**·I<sub>3</sub>·THF.

### Three **12**·I<sub>3</sub> solvates with THF, chlorobenzene and DCM

Donor **12** formed a series of **12**·I<sub>3</sub>·solvent radical cation salts by electrocrystallisation with tetrabutylammonium triiodide in THF, chlorobenzene or dichloromethane. Single crystal diffraction studies on crystals of all three substances showed that their monoclinic unit cells are very similar in dimensions. For all three cases the space group is *C*2, with one donor cation, a solvent molecule and two halves of two triiodide anions in the asymmetric unit; the central iodine atom of each triiodide ion lies on a crystallographic 2-fold axis. Aspects of the crystal structure of the THF solvate are shown in Fig. 4 and 5. The THF molecule is disordered between two orientations. The triiodide ions lie head-to-tail forming infinite rows along the *c* direction, with an I···I separation of 3.9363(5) Å and I-I···I angles of 174.22(3) and 177.14(2)°. The I···I separation is *ca.* 0.33 Å longer than the longest I···I separation in the triiodide salts of **11**. The donor cations occur in pairs related by a two-fold rotation axis with their TTF groups directly facing each other, and with S···S contacts between them of 3.272(4) and 3.306(4) Å; rows of these pairs lie between the rows of triiodides. The donor cations adopt a conformation with both naphthyl groups directed out perpendicular from the donor cation pair. The bulkier naphthyl side chains in donor **12**, rather than phenyl groups in donor **11**, prevent the formation of such compact donor cation pairs as in the salts of **11**. The donor cation retains the almost planar bonding geometry at nitrogen. The heterocyclic system of the donor cation species is very slightly bowed due to steric effects between donor cation side chains. One of the two crystallographically unique triiodides lies side-by-side with the four TTF units of two donor cation pairs, so that there are sixteen S···I contacts from as short as 3.586(2) and 3.592(2) Å up to 3.856(2) Å. The second triiodide lies among the chiral hydrocarbon sidechains of donor cations and is not involved in any short contacts. Donor cation pairs form rows, parallel to the triiodide chains, and interface to each other by roughly face-to-face  $\pi/\pi$  interactions between naphthyl groups whose mean planes lie at 16.1° to each other. The methyl group at the stereogenic centre prevents very close packing of the aromatic planes, though the outer edges of the rings do make C···C contacts in the range 3.40–3.46 Å. Naphthyl groups of donor cations in neighbouring rows interface in an edge-to-face manner, though the H···C




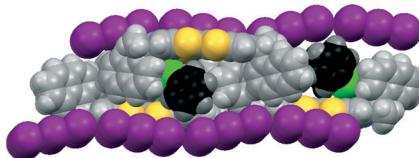


**Fig. 6** View of the structure of **12**·I<sub>3</sub>·chlorobenzene, showing how the solvent molecules lie close to the interface between triiodide ions.

contacts are not particularly short (2.9–2.97 Å). The THF molecules lie in cavities formed by several naphthalene rings and a TTF group, which are positioned just to one side of the point where two triiodide ions interface end-to-end.

The corresponding **12**·I<sub>3</sub> chlorobenzene solvate has a similar crystal structure (Fig. 6 and 7), but with chlorobenzene molecules filling the voids between the donor cation pairs. Indeed, there are Cl···benzene contacts between adjacent solvent molecules, Cl···centroid(benzene) = 3.429 Å, with the Cl···centroid vector roughly perpendicular to the benzene ring and a C–Cl···centroid angle of 148.9°, which link the solvent molecules in the *b* direction throughout the structure, perpendicular to the rows of triiodides and donor cation pairs. These chlorobenzene rows pass to one side of the perpendicular triiodide rows at just the point where the triiodide ions interface end-to-end, so that there are contacts from the two terminal iodine atoms to a *meta*-hydrogen of chlorobenzene of 3.23 and 3.35 Å. The unit cell is *ca.* 50 Å<sup>3</sup> larger than for the THF solvate, expanding along the *a* and *b* axes but contracting slightly along the *c* axis. The packing of the donor cations and triiodide anions has expanded somewhat, thus there are fourteen S···I contacts in the range 3.6390(15)–3.8517(15) Å compared to sixteen in the range 3.586–3.856 Å. However, the S···S contacts within a donor cation pair of 3.297(3) and 3.307(3) Å are very similar to those in the THF

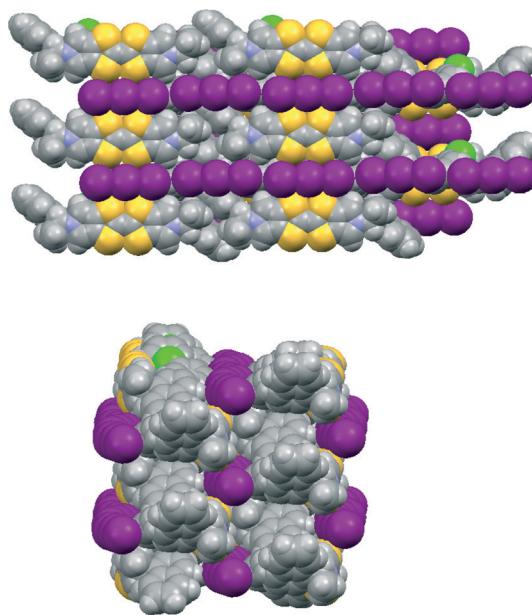

**Fig. 7** Crystal packing in **12**·I<sub>3</sub>·chlorobenzene viewed on the *bc* plane (above) and viewed along the *c* axis (below).

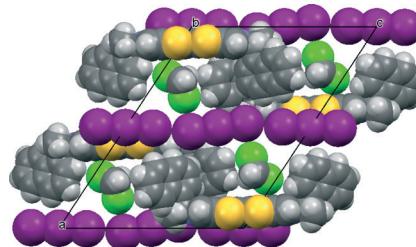


**Fig. 8** Crystal packing of **12**·I<sub>3</sub>·CH<sub>2</sub>Cl<sub>2</sub> viewed down the *b* axis with one orientation for the triiodide and associated dichloromethane molecule.

solvate (3.272 and 3.306 Å). Along the chain of triiodides the I···I separations are slightly longer (3.9887(5) *cf.* 3.9363 Å) and the I–I···I angles notably smaller (166.55(2) and 169.75(2) *cf.* 174.22 and 177.14°) than in the THF solvate, so the relative orientation of triiodide ions is further away from linear compared to the THF solvate, and thus compatible with the slightly shorter *c* axis.

The crystal of the dichloromethane solvate was twinned, but a reasonable model was refined (Fig. 8). The volume of the unit cell is very similar to that of the THF solvate. The overall organization of the crystal structure is very similar to the other solvates, however the smaller size of the solvent has provided the opportunity for one triiodide ion to adopt two different orientations, in a 3:1 ratio, which are coupled with two orientations of the dichloromethane molecule which can be accommodated in the ample solvent pocket. The components of the disordered triiodide share a common location for the central iodine atom, and the two orientations lie at *ca.* 9.8°.

### Salt **13**·I<sub>3</sub>

The salt of donor **13** with I<sub>3</sub><sup>–</sup> provides an unusual packing arrangement; the structure is not as well defined as for the

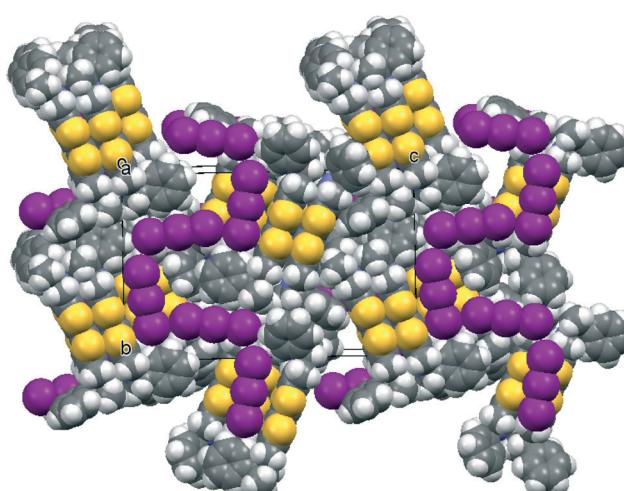

**Fig. 9** Packing arrangement of **13**·I<sub>3</sub> viewed in the *bc* plane showing the castellated arrangement of triiodide ions. Note that the apparent space between the castellated triiodides and phenyl groups is filled by phenyl rings from the next layer above.



other salts ( $R = 0.159$ ) even though a number of crystals were investigated with different X-ray sources, and so only the main features will be outlined. The cations and anions are packed together in layers perpendicular to the  $a$  axis with two layers per unit cell. Running through the layers in the  $b$  direction are castellated packing arrangements of triiodide ions with  $\text{I}\cdots\text{I}$  contacts of 3.812(7) and 4.000(9) Å and  $\text{I}\cdots\text{I}$  angles at the terminal I atoms of 92.2(2) and 111.8(2)° (Fig. 9). Two crystallographically independent donor cations form a face-to-face pair with their TTF planes lying perpendicular to the packing plane. Pairs are packed into bands extending along the  $b$  axis. There is considerable residual difference electron density concentrated around the triiodides suggesting extensive positional disorder. The Raman spectra for donor 13 and this salt (Table 4) are consistent with the +1 oxidation state.

## Conclusions

The crystal structures of 1:1 triiodide salts of enantiopure donors 11–13 show a range of packing arrangements involving donor cation pairs with triiodides which are arranged in head-to-tail pairs, continuous lines, and a castellated arrangement, but do not show the helical packing observed in the neutral donors 11 and 12. Future work will explore the incorporation of alternative non-linear ions. It may also be important to pay attention to the exact conditions for preparation of the salts. For enantiopure tetramethyl-BEDT-TTF, this has formed two phases with triiodide, a 1:1 phase with radical cation pairs separated by triiodides,<sup>3</sup> as for 11–13, but also a 2:~0.71 salt which, by comparison of its cell parameters with other salts, probably contains stacked donors.<sup>2</sup> If larger side chains are to be used to confer chirality it is likely to be preferable to prepare donors which have such features at only one end of the molecule.

## Experimental

### Preparation of radical cation salts

Two-compartment H-shaped cells with a volume of 40 ml were used to grow crystals by electrocrystallisation. Each cell had two platinum electrodes, separated by two porous glass frits to prevent contamination by reduction products. The electrodes were cleaned by washing in concentrated  $\text{HNO}_3$  followed by applying a voltage across the electrodes in 1 M  $\text{H}_2\text{SO}_4$  in each direction until the evolution of  $\text{H}_2$  and  $\text{O}_2$  was observed at the electrodes. Finally the electrodes were washed in distilled water and thoroughly dried. The cells were fixed inside sand-filled compartments to minimise vibration and were kept at ambient temperature. The donor (10 mg) was placed in one half of the cell and the cell was filled with a solution of tetrabutylammonium triiodide (120 mg) in 40 ml of solvent unless otherwise stated, and a constant current source was used to control the crystal growth rate.

### Conductivity measurements

Four-probe DC transport measurements were made on crystals of all triiodide salts, with the exception of 12· $\text{I}_3\text{-THF}$ , at room temperature using an Oxford Instruments Maglab System 2000. Gold wires (0.0025 mm diam.) were attached to the crystal, and the attached wires were connected to an eight-pin integrated circuit plug with carbon conductive cement (RS components). The resistance of the contacts was assumed to be negligible since the crystal had a high intrinsic resistance. Conductivity measurements on all five salts showed they were insulators.

### Raman spectroscopy

Raman spectra were recorded at room temperature with a Renishaw InVia Raman microscope equipped with a diode laser (785 nm) and a 1200  $\text{l mm}^{-1}$  grating using a laser power of *ca.* 1 mW. The recorded spectra are the result of 20 accumulations of 5 seconds each from 1200 to 1650  $\text{cm}^{-1}$  to observe the TTF  $\nu_3$  and  $\nu_4$  vibrations.

### X-Ray crystallography

Datasets for 11· $\text{I}_3$ , 12· $\text{I}_3\text{-THF}$  and 13· $\text{I}_3$  were measured at the EPSRC National Crystallography Service, University of Southampton,<sup>28</sup> using a Bruker-Nonius FR951 rotating anode, with collimation by 10 cm confocal mirrors, or in the case of 11· $\text{I}_3$  a graphite monochromator, and a Bruker-Nonius diffractometer APEX II diffractometer equipped with a CCD detector at 120 K. The dataset for 11· $\text{I}_3\text{-0.5THF}$  was measured with synchrotron X-radiation ( $\lambda = 0.6893$  Å) at Daresbury Laboratory SRS station 9.8, equipped with a silicon 111 monochromator and using a Bruker APEX2 CCD diffractometer at 120 K.<sup>29</sup> Datasets for 12· $\text{I}_3$ -chlorobenzene and 12· $\text{I}_3\text{-DCM}$  were measured at NTU on an Agilent Excalibur System equipped with Sapphire detector at 120 K. The crystal of 12· $\text{I}_3\text{-DCM}$  was twinned and the two components are related by the law: 1 0 1.438/0 -1 0/0 0 -1. Because of the difficulties in obtaining a satisfactory structure refinement, several crystals of 13· $\text{I}_3$  were investigated, some of them with synchrotron facilities at both SRS and Diamond Light Source beamline I19; these repeated attempts produced no improvement on the structure reported here, but did confirm the choice of crystal system and space group in preference to a twinned structure of lower symmetry. Structures were solved with SHELXS-97 and refined with SHELXL-97<sup>30</sup> using the X-SEED interface<sup>31</sup> and CRYSTALS.<sup>32</sup> Structures were refined with anisotropic atomic displacement parameters for non-hydrogen atoms, with the exception of 13· $\text{I}_3$ , where only iodine and sulfur atoms were treated anisotropically. Hydrogen atoms were placed geometrically and treated with a riding model. Geometric analyses were made with PLATON<sup>33</sup> and illustrations with MERCURY 3.3.<sup>34</sup>

### Acknowledgements

We thank the EPSRC for support (EP/C510488/1) and for funding the National Crystallography Service at Southampton



and Newcastle, and University College, London and Nottingham Trent University for a studentship (ACB). LM thanks the Royal Society for Research Grants (RG100853 and RG081209), International Exchange Scheme (IE130367), and International Joint Project (JP0869972). LM thanks the RSC for a Journals Grant for International Authors. We thank Mr. Brian O'Neill and Mr. Peter Moore for the construction of constant current sources, and STFC and Diamond Light Source for access to synchrotron facilities.

## References

- 1 J. D. Dunitz, A. Karrer and J. D. Wallis, *Helv. Chim. Acta*, 1986, **69**, 69–70; A. Karrer, J. D. Wallis, J. D. Dunitz, B. Hilti, C. W. Mayer, M. Bürkle and J. Pfeiffer, *Helv. Chim. Acta*, 1987, **70**, 942–953.
- 2 F. Pop, S. Laroussi, T. Cauchy, C. J. Gomez-Garcia, J. D. Wallis and N. Avarvari, *Chirality*, 2013, **25**, 466–474; S. Yang, F. Pop, C. Melan, A. C. Brooks, L. Martin, P. Horton, P. Auban-Senzier, G. L. J. A. Rikken, N. Avarvari and J. D. Wallis, *CrystEngComm*, 2014, **16**, 3906–3916.
- 3 M. Atzori, F. Pop, P. Auban-Senzier, R. Clérac, E. Canadell, M. L. Mercuri and N. Avarvari, *Inorg. Chem.*, 2015, **54**, 3643–3653.
- 4 E. Coronado, J. R. Galán-Mascarós, A. I. Coldea, P. Goddard, J. Singleton, J. D. Wallis, S. J. Coles and A. Alberola, *J. Am. Chem. Soc.*, 2010, **132**, 9271–9273.
- 5 G. L. J. A. Rikken, J. Fölling and P. Wyder, *Phys. Rev. Lett.*, 2001, **87**, 236602; G. L. J. A. Rikken and E. Raupach, *Nature*, 1997, **390**, 493–494; V. Krstić, S. Roth, M. Burghard, K. Kern and G. L. J. A. Rikken, *J. Chem. Phys.*, 2002, **117**, 11315–11319.
- 6 F. Leurquin, T. Ozturk, M. Pilkington and J. D. Wallis, *J. Chem. Soc., Perkin Trans. 1*, 1997, 3173–3178.
- 7 S. Yang, A. C. Brooks, L. Martin, P. Day, M. Pilkington, W. Clegg, R. W. Harrington, L. Russo and J. D. Wallis, *Tetrahedron*, 2010, **66**, 6977–6989.
- 8 I. Awheda, S. J. Krivickas, S. Yang, L. Martin, M. A. Guziak, A. C. Brooks, F. Pelletier, M. Le Kerneau, P. Day, P. N. Horton, H. Akutsu and J. D. Wallis, *Tetrahedron*, 2013, **69**, 8738–8750; L. Martin, J. D. Wallis, M. A. Guziak, J. Oxspring, J. R. Lopez, S. Nakatsuji, J. Yamada and H. Akutsu, *CrystEngComm*, 2014, **16**, 5424–5429.
- 9 R. J. Brown, A. C. Brooks, J.-P. Griffiths, B. Vital, P. Day and J. D. Wallis, *Org. Biomol. Chem.*, 2007, 3172–3182.
- 10 F. Pop, P. Auban-Senzier, A. Frackowiak, K. Ptaszyński, I. Olejniczak, J. D. Wallis, E. Canadell and N. Avarvari, *J. Am. Chem. Soc.*, 2013, **135**, 17176–17186.
- 11 C. Réthoré, N. Avarvari, E. Canadell, P. Auban-Senzier and M. Fourmigué, *J. Am. Chem. Soc.*, 2005, **127**, 5748–5749; A. M. Madalan, C. Réthoré, M. Fourmigué, E. Canadell, E. B. Lopes, M. Almeida, P. Auban-Senzier and N. Avarvari, *Chem. – Eur. J.*, 2010, **16**, 528–537.
- 12 M. Chas, M. Lemarié, M. Gulea and N. Avarvari, *Chem. Commun.*, 2008, 220–222; M. Chas, F. Riobé, R. Sancho, C. Minguillon and N. Avarvari, *Chirality*, 2009, **21**, 818–825.
- 13 F. Pop, P. Auban-Senzier, E. Canadell, G. L. J. A. Rikken and N. Avarvari, *Nat. Commun.*, 2014, **5**, 3757.
- 14 L. Martin, S. S. Turner, P. Day, K. M. A. Malik, S. J. Coles and M. B. Hursthouse, *Chem. Commun.*, 1999, 513; L. Martin, S. S. Turner, P. Day, P. Guionneau, J. A. K. Howard, K. M. A. Malik, M. B. Hursthouse, M. Uriuchi and K. Yakushi, *Inorg. Chem.*, 2001, **40**, 1363–1371.
- 15 L. Martin, P. Day, P. Horton, S. Nakatsuji, J. Yamada and H. Akutsu, *J. Mater. Chem.*, 2010, **20**, 2738–2742; L. Martin, P. Day, S. Nakatsuji, J. Yamada, H. Akutsu and P. Horton, *CrystEngComm*, 2010, **12**, 1369–1372.
- 16 E. Coronado, J. R. Galán-Mascarós, C. J. Gomez-Garcia, A. Murcia-Martinez and E. Canadell, *Inorg. Chem.*, 2004, **43**, 8072–8077.
- 17 J. A. Schlueter, B. H. Ward, U. Geiser, H. H. Wang, A. M. Kini, J. Parakka, E. Morales, H. J. Koo, M. H. Whangbo, R. W. Winter, J. Mohtasham and G. L. Gard, *J. Mater. Chem.*, 2001, **11**, 2008–2013.
- 18 E. Coronado, S. Curreli, C. Giménez-Saiz, C. J. Gómez-García, P. Deplano, M. L. Mercuri, A. Serpe, L. Pilia, C. Faulmann and E. Canadell, *Inorg. Chem.*, 2006, **46**, 4446–4457.
- 19 F. Riobé, F. Piron, C. Réthoré, A. M. Madala, C. J. Gómez-García, J. Lacour, J. D. Wallis and N. Avarvari, *New J. Chem.*, 2011, **35**, 2279–2286.
- 20 L. Martin, P. Day, H. Akutsu, J.-I. Yamada, S.-I. Nakatsuji, W. Clegg, R. W. Harrington, P. N. Horton, M. B. Hursthouse, P. McMillan and S. Firth, *CrystEngComm*, 2007, 865–867.
- 21 N. Avarvari and J. D. Wallis, *J. Mater. Chem.*, 2009, **19**, 4061–4076; E. Coronado and J. R. Galán-Mascarós, *J. Mater. Chem.*, 2005, **15**, 66–74.
- 22 S. Yang, A. C. Brooks, L. Martin, P. Day, H. Li, P. Horton, L. Male and J. D. Wallis, *CrystEngComm*, 2009, 993–996.
- 23 M. R. Tomesi and F. J. Stoddart, *J. Org. Chem.*, 2007, **72**, 9335–9338; B. W. Laursen, S. Nygaard, J. O. Jeppesen and F. J. Stoddart, *Org. Lett.*, 2004, **6**, 4167–4170.
- 24 R. C. Teitelbaum, T. J. Marks and C. K. Johnson, *J. Am. Chem. Soc.*, 1980, **102**, 2986–2989; K. Honda, M. Goto, M. Kurahashi, H. Anzai, M. Tokumoto, H. Bando and T. Ishiguro, *Bull. Chem. Soc. Jpn.*, 1987, **60**, 782–784; D. V. Konarev, S. S. Khasanov, A. Otsuka, G. Saito and R. N. Lyubovskaya, *Synth. Met.*, 2005, **151**, 231–238.
- 25 M. A. Guziak, J. D. Wallis and L. Martin, paper in preparation.
- 26 S. C. Nyberg and C. H. Faerman, *Acta Crystallogr., Sect. B: Struct. Sci.*, 1985, **41**, 274–279.
- 27 S. Matsuzaki, T. Moriyama and K. Toyoda, *Solid State Commun.*, 1980, **34**, 857–859; M. Miizutani, K. Tanaka and K. Kawabata, *Synth. Met.*, 1991, **44**, 321–325; H. H. Wang, J. R. Ferraro, J. M. Williams, U. Geiser and J. A. Schlueter, *J. Chem. Soc., Chem. Commun.*, 1994, 1893–1894; I. Olejniczak, A. Frackowiak, J. Matysiak, A. Madalan, F. Pop and N. Avarvari, *Cent. Eur. J. Phys.*, 2013, **12**, 215–220.
- 28 S. J. Coles and P. A. Gale, *Chem. Sci.*, 2012, **3**, 683–689.
- 29 R. J. Cernik, W. Clegg, C. R. A. Catlow, G. Bushnell-Wye, J. V. Flaherty, G. N. Greaves, I. Burrows, D. J. Taylor, S. J. Teat



and M. Hamichi, *J. Synchrotron Radiat.*, 1997, **4**, 279–286; R. J. Cernik, W. Clegg, C. R. A. Catlow, G. Bushnell-Wye, J. V. Flaherty, G. N. Greaves, I. Burrows, D. J. Taylor, S. J. Teat and M. Hamichi, *J. Synchrotron Radiat.*, 2000, **7**, 40.

30 G. M. Sheldrick, *Acta Crystallogr., Sect. A: Found. Crystallogr.*, 2008, **64**, 112–122.

31 L. J. Barbour, *J. Supramol. Chem.*, 2001, **1**, 189–191.

32 P. W. Betteridge, J. R. Carruthers, R. I. Cooper, K. Prout and D. J. Watkin, *J. Appl. Crystallogr.*, 2003, **36**, 1487.

33 A. L. Spek, *Acta Crystallogr., Sect. D: Biol. Crystallogr.*, 2009, **65**, 148–155.

34 C. F. Macrae, P. R. Edgington, P. McCabe, E. Pidcock, G. P. Shields, R. Taylor, M. Towler and J. van de Streek, *J. Appl. Crystallogr.*, 2006, **39**, 453–457.

