

CrossMark
click for updatesCite this: *RSC Adv.*, 2015, 5, 28410

Effect of graphene content on the properties of poly(lactic acid) nanocomposites

Ravi Babu Valapa, G. Pugazhenthil* and Vimal Katiyar*

In the current work, the influence of temperature on the exfoliation of expandable graphite (EG) and its structural properties were investigated in detail. The EG exfoliated at 750 °C was subjected to sonication and further used as reinforcement material in the poly(lactic acid) (PLA) matrix to investigate the influence of "graphene" (GR) on the structural, morphological, thermal, optical, mechanical and oxygen barrier properties of PLA composites. X-ray diffraction results disclose the effect of sonication time on the dispersion ability of GR in the PLA matrix. A high resolution transmission electron microscopy image of GR demonstrates a monolayer structure of GR. Thermo-gravimetric analysis reveals that the T_{onset} value for the PLA composite with 0.5 wt% GR content increases by 6 °C over neat PLA, when 10% weight loss is taken as a point of comparison. The increase in the thermal stability of PLA composites is also verified by an increase of activation energy (E_a) value evaluated by the Coats–Redfern method. Differential scanning calorimetry analysis confirms that GR acts as a nucleating agent that enhances the melting point of PLA composites over neat PLA. The enhancement of tensile strength (17%) and elongation at break (51%) is obtained for PLA composites over neat PLA.

Received 2nd December 2014
Accepted 3rd March 2015

DOI: 10.1039/c4ra15669b

www.rsc.org/advances

Introduction

Poly(lactic acid) (PLA) is versatile eco-friendly polyester that can be manufactured from precursors made of renewable resources, especially starch rich products such as corn, wheat, and sugar beet.¹ The blooming of innovative technologies for massive production with cheaper processing costs facilitates PLA to occupy a vital position in the market of sustainable polymers. PLA is currently explored as a sustainable alternative to petrochemical derived polymers of fossil fuel origin and hence possesses massive potential for application in the field of commodity areas like packaging.² Nevertheless, it is necessary to tailor the gas barrier and flexural characteristics of PLA in order to really substitute the benchmark packaging materials, namely polyolefins and poly(ethylene terephthalate) (PET). The common strategies that are usually pursued to attain these objectives include the addition of plasticizers,^{3,4} blending with other polymers^{5,6} and incorporation of nanofillers.^{7–9} The latter is deemed to be an interesting option, because a small percentage of nanofiller addition can significantly improve the target properties, while keeping the properties of PLA intact. PLA composites with amended properties (mechanical stability, thermal stability and low gas permeability) have been reported with the addition of various nanofillers, namely clays,¹⁰ layered silicates,¹¹ carbon nanotubes (CNTs),¹² citrate esters.¹³ PLA

composites reinforced with carbonaceous nanofillers like CNTs are evidenced to reveal a noteworthy balance of properties in terms of mechanical, thermal and barrier effects.¹⁴ However, the high cost factor associated with CNTs limit their widespread applications in industrial corners and hence, additional proxies need to be prospected.

Recently, graphene has been recognized as potential nanofiller for the production of polymer nanocomposites. It is chemically similar to CNTs and structurally similar to silicate layers.¹⁵ This material exhibits supernatural properties like extremely high mechanical strength (Young's modulus = 1 TPa, tensile strength = 130 GPa), and thermal conductivity (5000 W m^{−3} K^{−1}), which bounds above the standards testified for single-walled CNTs. Beside the extremely high surface area (2630 m² g^{−1}), these properties along with gas impermeability revealed the prospective applications of graphene for upgrading the mechanical, thermal as well as gas barrier characteristics of polymeric materials.^{16–23} The advantage of selecting 2D nanofillers as reinforcement in the PLA matrix is twofold: (i) when nanoscale graphene sheets are well dispersed in the PLA matrix, the tremendous aspect ratio provided by this filler could contribute to PLA chain confinement effects leading to improvement in stiffness and strength, (ii) the nanoscale filler being layered structures can provide a zigzag torturous diffusion path leading to enhancement in barrier performance for gas, moisture and oxygen transmissions.

When the graphene is uniformly dispersed in the polymer matrix, the target properties can be improved at comparatively lower loading than conventional carbon reinforcements.

Department of Chemical Engineering, Indian Institute of Technology Guwahati, Guwahati – 781039, Assam, India. E-mail: pugal@iitg.ernet.in; vkatiyar@iitg.ernet.in; Fax: +91 361 2582291; Tel: +91 361 2582264; +91 361 2582278

However, so far, the exfoliation of graphite to graphene and its reinforcement into polymeric materials has not been completely fruitful. Owing to the existence of strong van der Waals interactions (2 eV nm^{-2}) between the interlayer spacing, it is indeed tough to attain a completely alienated state of graphene.^{24,25} Several research works have been endeavored describing the exfoliation and optimization of the dispersion of graphite sheets *via* the process of intercalation of alkali metals between the carbon layers²⁶ or by subjecting the same to strong acidic treatment.^{27–29} The interlayer spacing has also been expanded *via* heat treatment or microwave irradiation subsequently trailed by mechanical crushing.³⁰ The process of expansion led to considerable enhancement in the surface area of graphite, as a consequence of which, advancement in the inherent properties of the polymeric matrix are evidenced.^{25,31,32} Murariu and co-workers investigated the addition of expandable graphite (EG) on the properties of PLA composites prepared by the melt compounding method.³⁰ In their study, complete exfoliation of EG into graphene sheets was not achieved, as a result, the tensile strength of the PLA composites exhibited downturn with an increase of EG (%wt) loading in the PLA matrix. To the best of our knowledge, study on optimization of exfoliation temperature for GR synthesis and highlighting the performance of PLA/GR composites synthesized *via* solution casting method have not been reported. In this work, EG is subjected to exfoliation at different temperatures ranging from 200–1000 °C and the optimum temperature for exfoliation is identified based on carbon yield (%) and bulk density (kg cm^{-3}) of the resultant exfoliated graphite (EXG). Then, sonication technique is adopted to completely exfoliate the EXG into graphene sheets (GR). Thereafter, PLA–GR composites with various content of GR are synthesized *via* solution casting method and resultant films are characterized in detail to emphasize their performance.

Experimental

Materials

Expandable graphite (EG, 99.9%) was obtained from Asbury Carbons (USA). The catalog number for EG is “Asbury 3772” (particle size: 300 μm , carbon: 99%, expansion ratio (mL g^{-1}) min: 270, pH range: 5–10, intercalates: sulfuric acid, nitric acid, hydrogen peroxide, potassium permanganate). Poly(lactic acid) (grade: 2003D) obtained from Nature work® was used as the bio-polymer matrix. Heat distortion temperature, melt flow index (g per 10 min) at 260 °C and specific gravity for PLA is 55 °C, 6 and 1.24, respectively. Chloroform obtained from Merck (India) Ltd., was used as the solvent for synthesizing poly(lactic acid)–graphene (PLA–GR) composites.

Exfoliation of expandable graphite (EG)

Accurately, 0.05 g of EG was weighed and placed in a silica crucible. Thermal exfoliation of expandable graphite was carried out at different temperature ranging from 200 to 1000 °C in an air atmosphere. The crucible containing expanded graphite was inserted in a muffle furnace (which was already set

at a desired temperature) for 2 min in order to obtain exfoliated graphite samples (EXG 200–1000 °C). After thermal treatment, an expansion volume was measured using a measuring cylinder. The actual reason for exfoliation is the increase in volume, and the resultant pressure, caused by the rapid heating of the intercalated compound. The following relations were used to calculate bulk density and carbon yield (%)

$$\text{Bulk density} = \frac{\text{mass of the exfoliated graphite}}{\text{volume of the exfoliated graphite}} \quad (1)$$

$$\text{Carbon yield (\%)} = \frac{\text{mass of the exfoliated graphite}}{\text{mass of the expandable graphite}} \quad (2)$$

Preparation of PLA–GR composites

PLA–GR composites were fabricated by a simple solution-casting method as follows: at first, PLA ($\sim 0.95 \text{ g}$) was dissolved in 30 mL of chloroform with continuous stirring for 2 h in order to completely dissolve the PLA (Solution A). Graphene (0.1, 0.3, 0.5 wt% with respect to PLA) was dispersed in chloroform (20 mL) separately by bath sonication for 30 min separately (Solution B). Subsequently, the solution containing dispersed GR (Solution B) was transferred into PLA–chloroform mixture (Solution A) and further subjected to bath sonication (Make: Elma and Model: T460) for 15 min and 30 min (Solution C). The corresponding photographs of Solution A, B and C are portrayed in Fig. 1. Finally, the PLA–GR solution was casted on Teflon petriplates and further, dried under ambient conditions for 24 h. The dried composite films were peeled off carefully from the petriplates. The resulting films were finally dried in a vacuum at 40 °C for 12 h. The obtained films were stored in airtight bags at room temperature for further characterizations. The thickness of the fabricated films was measured using a film

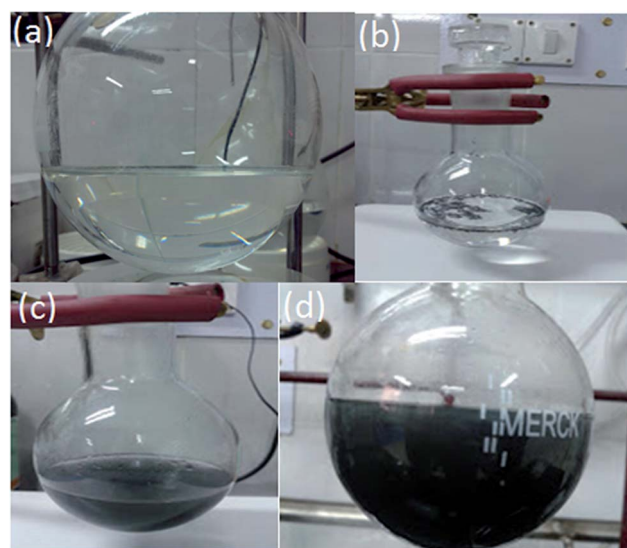


Fig. 1 (a) PLA (Solution A), (b) EXG 750 in chloroform before sonication (Solution B), (c) EXG in chloroform after sonication (Solution B) and (d) PLA–GR composites (Solution C).

thickness meter (indi 6156, India). Twenty measurements were taken on each film and the average thickness of the films was found in the range of $60 \pm 10 \mu\text{m}$. Thereafter, all the compositions were designated as neat PLA, PLA-GR-0.1, PLA-GR-0.3, and PLA-GR-0.5 for PLA, PLA/graphene 0.1 (wt%), PLA/graphene 0.3 (wt%), and PLA/graphene 0.5 (wt%), respectively.

Characterization

X-ray diffraction analysis (XRD)

XRD analysis of neat PLA and composite films were carried out under air atmosphere at room temperature on a Bruker A8 advance instrument using Cu-K α ($\lambda = 0.15406 \text{ nm}$) radiation operating at 40 kV and 40 mA. The diffraction data were recorded in the 2θ range of $1\text{--}50^\circ$ with a scanning rate of $0.05^\circ \text{ s}^{-1}$ and 0.5 s step size.

BET surface area analysis

Nitrogen physisorption measurements were conducted on a Beckman Coulter surface area analyzer (COULTER SA 3100 model). The samples were degassed at 105°C for 4 h prior to N_2 adsorption-desorption measurements. The specific surface area was calculated by BET (Brunauer, Emmett, and Teller) model. The total pore volume was estimated at a relative pressure of 0.99, assuming that full surface saturation has been achieved with nitrogen.

Morphological analyses

The morphology and the selected area diffraction (SAED) pattern of graphene were visualized using transmission electron microscopy (JEOLJEM 2100) operated at 200 kV. By direct casting of graphene solution over the carbon-coated copper TEM grid, images of the same were obtained. The morphology of PLA-GR composites was pictorialized using field-emission type scanning electron microscopy (Zeiss Sigma model) operated at 2 kV. The dispersion of GR in PLA composites was investigated by Leica DM 2500P polarizing optical microscope fitted with a QICAM FAST1394 camera.

Thermogravimetric analysis (TGA)

Thermogravimetric analysis was performed on a Mettler Toledo thermo gravimetric analyzer (TGA/SDTA 851 $\text{\textcircled{R}}$ model). Samples ($10.5 \pm 0.3 \text{ mg}$) were placed in a 900 μL crucible. Neat PLA and PLA-GR composites were heated from 25 to 700°C in a 60 mL min^{-1} flow of N_2 at a heating rate of $10^\circ\text{C min}^{-1}$.

Differential scanning calorimetry (DSC)

Thermal properties and crystallization behavior of PLA and PLA-GR composites were studied using a differential scanning calorimeter (Mettler Toledo-1 series). Samples ($10 \pm 0.5 \text{ mg}$) were hermetically sealed in aluminum pans and heated from 25 to 180°C at a heating rate of 5°C min^{-1} in the N_2 atmosphere (N_2 flow rate of, 50 mL min^{-1}). All the samples were first heated from 25 to 180°C and held at this temperature for 5 min to eliminate the effect of thermal and processing history. Glass

transition temperature (T_g), cold crystallization temperature (T_c), enthalpy change at T_c (ΔH_c), melting temperature (T_m) and enthalpy of fusion at T_m (ΔH_m) for neat PLA and composite samples were determined from the DSC thermograph during the second heating cycle. The percentage crystallinity ($\% X_c$) of PLA was calculated according to the following relation.

$$\%X_c = \frac{(\Delta H_m - \Delta H_c)}{(\Delta H_{mp})} \times 100\% \quad (3)$$

where, ΔH_m is enthalpy of fusion at melting temperature (T_m), ΔH_c is the enthalpy of fusion at cold crystallization temperature (T_c). ΔH_{mp} is the heat of fusion of a perfect PLA crystal (93.6 J g^{-1}).³⁴

UV-visible spectrophotometer analysis

Transparency measurement for composite films was carried out using UV-visible spectrophotometer (Make: Perkin Elmer, Model: Lambda 35). The wavelength range was varied between $200\text{--}600 \text{ nm}$ with a scan rate of 50 nm min^{-1} and a spectral bandwidth of 2 nm .

Mechanical testing

The tensile properties such as tensile strength and elongation-at-break were measured under ambient temperature conditions with a 50 kN load cell on a tensile tester (Make: Kalpak instruments, Model: KIC-2-050-C, India). The cross-head speed was fixed as 5 mm min^{-1} . Average specimen parameters were: thickness of 0.06 mm , width of 10 mm and length of 50 mm . Three specimens for each sample were subjected for testing and the average values were reported. The ASTM standard D 882-12 was followed for preparation of the dumb-bell shaped samples used in this test.

Results and discussion

Effect of temperature on exfoliation

The influence of temperature on exfoliation of EG in terms of volume exfoliated, weight after exfoliation, bulk density and carbon yield are presented in the Table 1. It is clearly seen from Table 1 that the volume of expandable graphite (EG) increases with increasing temperature up to 750°C . This is due to the maximum swelling of intercalates taking place at 750°C that increases the interlayer distance between graphene sheets resulting in high volume of expansion. After 750°C , the expansion volume decreases, owing to the removal of intercalates from interlayers.²⁸ Hence, it is clear that only swelling of intercalates occurs in the interlayers when the EG is subjected to thermal shock in the temperature range of $200\text{--}750^\circ\text{C}$. After 750°C , a significant difference in weight is observed which is found to be in correspondence with carbon yield (%) values. The rapid decrease in weight is due to evaporation of intercalates as gaseous products such as CO_2 and SO_2 .²⁸ It is also important to be noticed that the carbon yield (%) value drops down after 750°C . An increase in exfoliation temperature above 750°C leads to the reduction in the bulk density indicating that the imparted heat is enough for evaporation of intercalated

Table 1 Effect of temperature on exfoliation of EG^a

Sample name	Volume exfoliated (mL)	Weight after exfoliation (g)	Bulk density (kg cm ⁻³)	Carbon yield (%)
EXG 200	0.1	0.05	500	100
EXG 300	3	0.046	15.33	92
EXG 400	4.5	0.043	9.56	86
EXG 500	9	0.041	4.55	82
EXG 600	12.5	0.041	3.28	82
EXG 700	15	0.041	2.73	82
EXG 750	15.5	0.040	2.58	80
EXG 800	14	0.034	2.43	68
EXG 900	12	0.023	1.92	46
EXG 1000	4	0.007	1.75	14

^a EXG 200 represents the EG exfoliated at 200 °C.

substance and sample expansion. Even though, the least bulk density value might correspond to a maximum increase in exfoliation rate; two other factors (the volume of exfoliation and carbon yield) should be taken into consideration for optimization of temperature. In the present study, it is considered that 750 °C is the optimum condition for thermal exfoliation based on the information obtained from exfoliation volume, carbon yield, and bulk density. However, no significant change in weight is noticed after exfoliation at the temperature ranging between 200 and 750 °C. Table 1 clearly reveals that 80% of carbon yield is obtained at an exfoliation temperature of 750 °C.

Characterization of expandable graphite (EG), exfoliated graphite (EXG) and graphene (GR)

XRD analysis. The XRD patterns of EG and EXG samples are depicted in Fig. 2. EG exhibits a sharp diffraction peak (0 0 2) at 26.52° indicating that EG is a sort of graphite intercalation compound (GIC). The basal peak position remains same for EG in comparison to natural graphite reported in the literature.^{28,33,35,36} This signifies that carbon crystal layer, which is the elementary constituent, does not undergo any change after intercalation. When all the EXG samples are subjected to XRD

analysis, no significant deviation in the peak position (26.52°) is observed (Fig. 2). Nevertheless, the peak intensity (26.52°) gradually decreases when compared to EG with an increase in exfoliation temperature. This represents that lower the peak intensity, higher will be the degree of exfoliation subject to the same sample loading and packing density.³⁶

Surface area analysis. Nitrogen (N₂) adsorption–desorption isotherms are shown in Fig. 3. In the isotherm pattern observed for the EG sample, the convexity suggests that adsorption of N₂ takes place by cooperative mechanism. It means that adsorbate–adsorbent interaction is less importance than adsorbate–adsorbate interaction in nonporous materials like EG. Because of weak interaction between N₂ and EG, the isotherm curve is flat in the initial P/P_0 regions. Nevertheless, once adsorption of the N₂ molecule begins, N₂–N₂ interaction tends to aggrandize the adsorption of more N₂ molecules thus translating the isotherm to be convex with respect to the relative pressure values in the abscissa. With respect to increase in exfoliation temperature, type III isotherm gradually changes to type II pattern, which is the characteristic feature like EXG.³⁷ Type II isotherm pattern observed for EXG samples is indicative of enhanced interaction between N₂ and EXG, which is confirmed by the presence of knee portion in the initial P/P_0 region for all

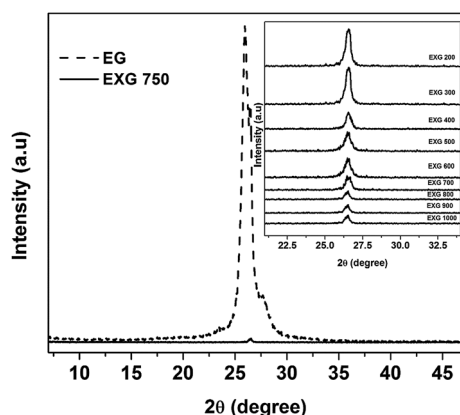


Fig. 2 XRD patterns of expandable graphite (EG) and exfoliated graphite (EXG).

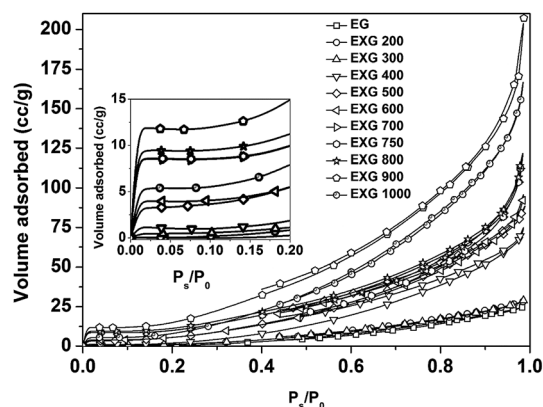


Fig. 3 N₂ adsorption–desorption isotherms for expandable graphite (EG) and exfoliated graphite (EXG).

the EXG samples. It can be perceived from the inset graph (Fig. 3), that increase in intercept (c) value or knee region for EXG samples with respect to exfoliation temperature occurs up to 900 °C. In general, greater the surface area, maximum will be the exfoliation.³⁵

BET surface area and pore volume of the EXG samples are presented in the Table 2. Surface area and the pore volume increase with an increase in exfoliation temperature. This behavior reveals that pores are created in the graphite surface due to the removal of intercalates that escape from the graphitic interlayers during exfoliation.^{38–40} The maximum surface area ($51.32 \text{ m}^2 \text{ g}^{-1}$) and pore volume ($0.29 \text{ cm}^3 \text{ g}^{-1}$) are obtained for EXG 900 sample that signifies the maximum degree of exfoliation. However, the surface area, intercept (c) and volume of N_2 adsorbed are reduced for EXG-1000 sample. This is because of restacking of graphene layers due to the complete removal of intercalates after exfoliation at 1000 °C. Although, a maximum surface area obtained for EXG 900, carbon yield (%) is drastically reduced to 46%. Considering this fact, 750 °C is chosen as the optimum exfoliation temperature and hence, EXG-750 is utilized as a source for the synthesis of GR and PLA-GR composites.

Morphological analyses. The morphological images of EG and EXG samples are depicted in Fig. 4. EG is partially oxidized form of graphite containing intercalated compounds between graphene layers, as shown in Fig. 4(a). EG can undergo exfoliation when subjected to sudden thermal shock at a desired temperature. In case of Fig. 4(b), it can be observed that exfoliation of EG is just initiated due to the insufficient exfoliation temperature (200 °C). Fig. 4(c) and (d) show selected FE-SEM micrographs of the EXG 750 sample at different magnifications. These images elucidate that EG is exfoliated several hundred times along with the c -axis. This results in a massive increase in volume of EG. Origin of this process lies in the vaporization of the intercalate indicating that gaseous products cause the explosive expansion of the EG.⁴¹ After expansion, graphite becomes porous structure material with improved surface area comprising of many sheets of nanometer thickness.

The morphology and SAED patterns of GR are visualized by HRTEM as depicted in Fig. 4(e) and (f). The HRTEM image (Fig. 4(e)) pictorialized after sonication demonstrates a

monolayer structure. This suggests that, the graphene sheet obtained after sonication process is indeed a monolayer GR. Fig. 4(f) depicts the selected area electron diffraction (SAED) pattern of graphene, which is recorded by selecting a specified area from the graphene sheet slung overhead to a micrometer-sized hole on a 200 mesh copper grid. This clearly displays the crystalline structure of GR. The inner six member ring corresponds to the (1100) plane, whereas six intense dots are ascribed to the [0001] diffractions.^{41,42} The diffraction pattern images confirm that the resulted graphene retains the hexagonal symmetry of carbon framework.

Characterization of PLA-GR composites

XRD analysis. XRD analysis of neat PLA and its composites is carried out to determine the crystallographic properties of the PLA composites. The diffractograms recorded for PLA composite samples prepared with 15 and 30 min sonication are illustrated in Fig. 5(a) and (b), respectively. A scattered intense distribution with a broad peak observed at $2\theta \approx 16.7^\circ$ corresponds to the reflections of (1 1 0) and (2 0 0) planes of orthorhombic α -crystalline phase of PLA.⁴³ In all the composites, the peak position ($2\theta = 16.7^\circ$) corresponding to the crystal structure of PLA is not altered. Hence it is clear that lattice parameters are not altered with the incorporation of GR. However, it is clearly seen from Fig. 5(a) that a sharp peak appears at 26.5° corresponding to the (0 0 2) graphitic carbon structure.^{28,33,36} This ratifies the existence of pure graphite in the form of stacked GR sheets, suggesting that 15 min sonication applied during the synthesis of PLA-GR solution is not sufficient enough to completely exfoliate the graphene layers. Also some of the graphene sheets may persist in the aggregate conformation. To overcome this issue, 30 min sonication was applied during the synthesis of PLA-GR composites and the XRD profiles of the composites are depicted in the Fig. 5(b). It is clear from Fig. 5(b) that no peak appeared at $2\theta = 26.5^\circ$ corresponding to graphite. This is ascribed to the annoyance of ordered graphitic structure. These results elucidate that the graphite has been successfully exfoliated into single- or few-layers of stacking platelets and also completely dispersed in the PLA matrix. In the work reported by Esmail *et al.*,⁴⁴ and Marius *et al.*,³³ on PLA-nanographite platelet (NGP) and PLA-expanded graphite composites, respectively prepared *via* melt-compounding process, the XRD results confirmed the presence of the graphitic peak at 2θ value of 26.5° for all the composite systems. This suggests the fact that the melt-compounding used in their study could not completely exfoliate or isolate the graphene layers and several platelets existed in the amassed form, which in turn affected the mechanical properties. In reality, as the graphene nanosheets in EG are always interlinked with each other, “complete exfoliation” has no sense as in the case like organically modified layered silicates (OMLS).³³ However, a conclusion can be drawn from the current study that the sonication used for separating the interlinked nanosheets of EXG has the effect on the exfoliation as well as the dispersion quality of graphene sheets in the PLA matrix. Based on the XRD analysis, now it is known that 30 min sonication (during the preparation of PLA-GR solution)

Table 2 Surface area characteristics for EG and EXG obtained at different temperatures

Sample name	S_{BET} ($\text{m}^2 \text{ g}^{-1}$)	Pore volume ($\text{cm}^3 \text{ g}^{-1}$)
EG	0	0.0429
EXG 200	0	0.0429
EXG 300	5.881	0.0434
EXG 400	19.413	0.1285
EXG 500	19.732	0.1299
EXG 600	20.198	0.1375
EXG 700	33.459	0.1755
EXG 750	36.325	0.1762
EXG 800	38.411	0.1769
EXG 900	51.321	0.2912

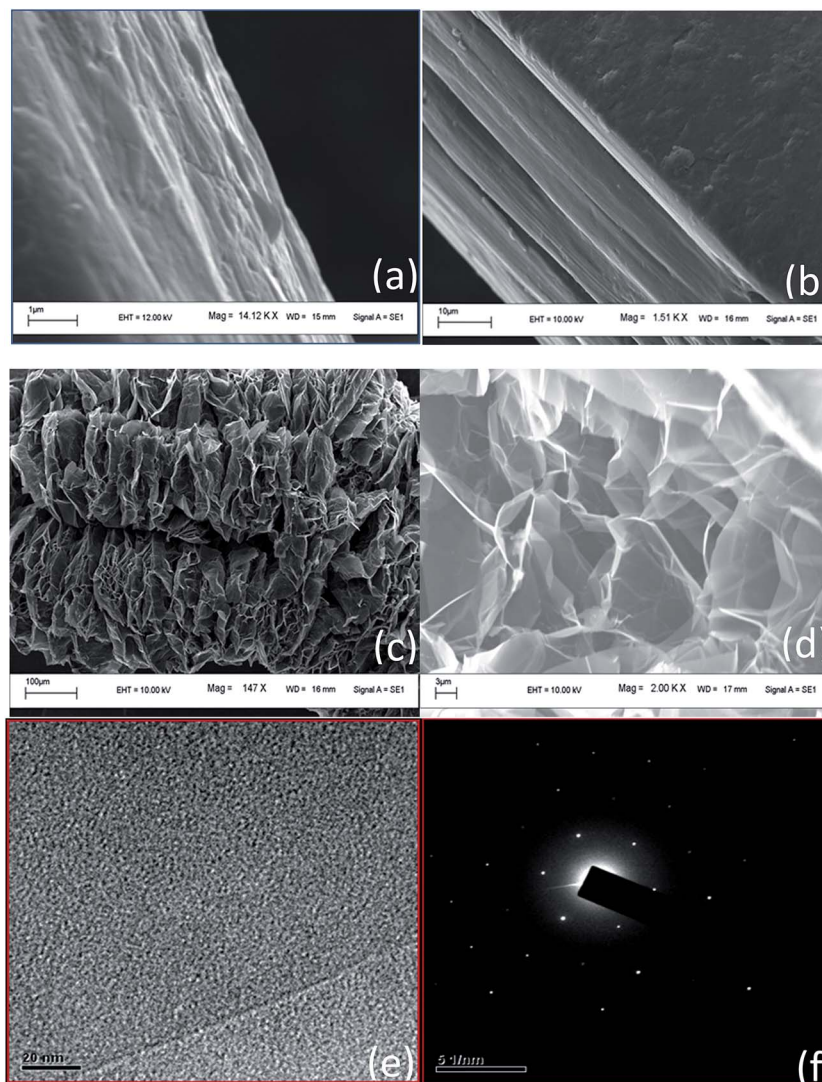


Fig. 4 FE-SEM images of (a) expandable graphite, (b) EXG 200, (c) EXG 750 (low magnification), (d) EXG 750 (high magnification), (e) HRTEM image of GR and (f) SAED pattern of GR.

disperses GR well in the PLA matrix and hence further analyses are carried out for the samples prepared with 30 min sonication.

Morphological analyses. The dispersion of graphene sheets in the polymer matrix and their interfacial bonding are vital features that influence the enhancement of physical and mechanical properties of the composite materials. In order to evidence the dispersion of GR in the PLA matrix, FE-SEM and TEM analysis is performed using PLA-GR composite films and the images are shown in Fig. 6. It is clear from Fig. 6 that GR sheets are arbitrarily dispersed in the PLA matrix. These results are in good agreement with the XRD patterns of PLA-GR composites (see Fig. 5), where the peak corresponding to the graphite layer structure at 26.5° is not observed even at higher loadings of GR. These results suggest that the dispersion of GR in PLA matrix is near to a single sheet level. Aggregation of EG in PLA matrix was reported by Marius *et al.*³³ This is in contrast to the present study, where GR sheets are not restacked in the PLA

matrix, which might be due to the effectiveness of the sonication process used for the synthesis of PLA-GR composite.

The morphology of the PLA and PLA-GR composites is also investigated using the polarized optical microscopy to know the dispersion of GR in the PLA matrix. Fig. 7 shows the optical reflection micrographs of PLA composites with the various GR contents. The black portion is the GR sheets and the background is the polymer matrix. It is seen that, at the microscopic level, the GR sheets display a homogeneous distribution in the form of nanosheet clusters throughout the PLA matrix. As the content of the GR increases, the black portion of the micrograph also increases.

Thermo gravimetric analysis. In order to cognize the influence of GR content on the thermal stability of PLA matrix, TGA analysis is carried out for PLA and PLA-GR composites. Fig. 8 depicts the temperature-dependent (TGA) and derivative weight loss profiles (DTG) for PLA and PLA-GR composites carried out under nitrogen atmosphere at a heating rate of $10^\circ\text{C min}^{-1}$. It

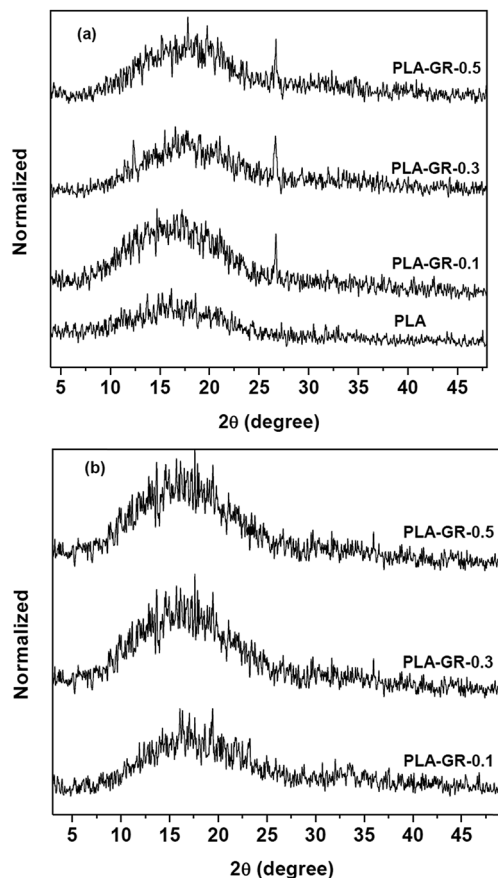


Fig. 5 XRD patterns of neat PLA and PLA-GR composites prepared with (a) 15 min sonication and (b) 30 min sonication time.

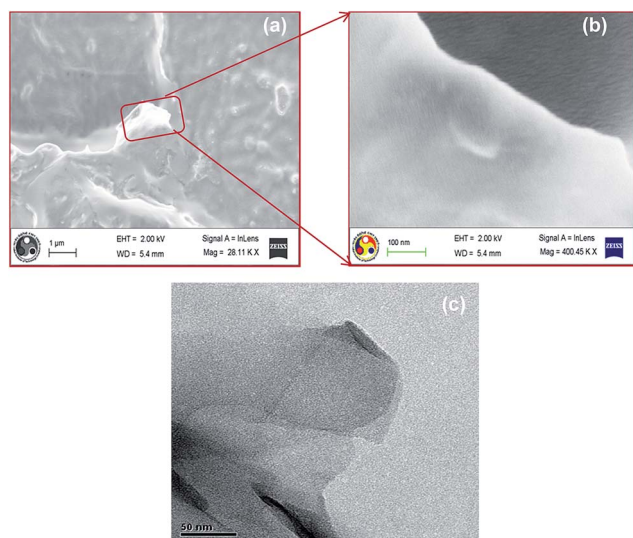


Fig. 6 FE-SEM images of (a) PLA-GR composite (low magnification) (b) PLA-GR composites (high magnification) and (c) TEM image of PLA-GR-0.1.

is important to mention that % weight loss for the PLA and PLA-GR composites samples are calculated after water loss as shown in Fig. 8(a). The main thermal degradation process of

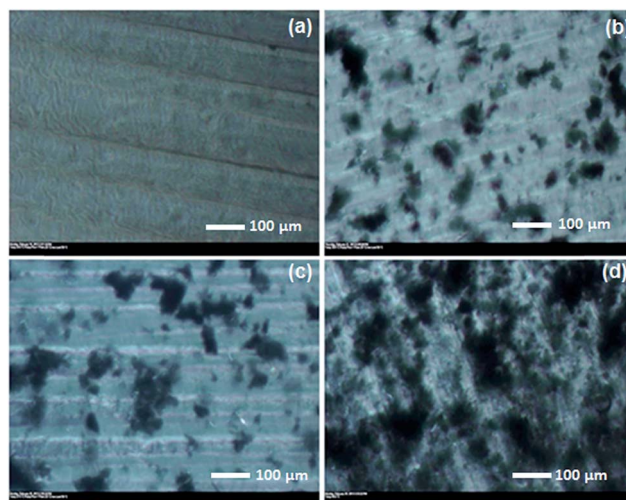


Fig. 7 Optical microscopy images of (a) PLA, (b) PLA-GR-0.1, (c) PLA-GR-0.3 and (d) PLA-GR-0.5.

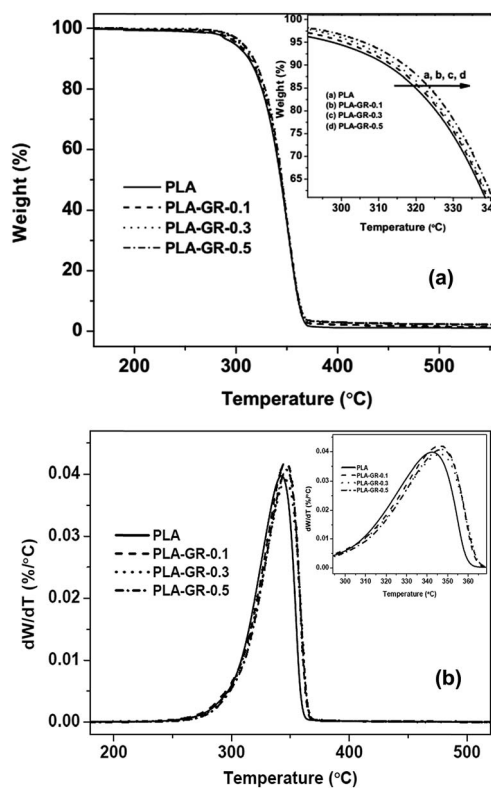


Fig. 8 (a) TGA and (b) DTG curves of neat PLA and PLA-GR composites.

PLA begins at temperature above 300 °C, which is principally attributed to intra-molecular *trans*-esterification (backbiting reaction).^{45–50} When 10% weight loss is taken as a point of comparison, T_{onset} is found to be 311, 313, 315 and 317 °C for PLA, PLA-GR-0.1, PLA-GR-0.3 and PLA-GR-0.5, respectively. The obtained results clearly specify that the PLA-GR-0.5 composite exhibits around 6 °C improvement in thermal

stability over neat PLA. The decomposition temperature at 50% weight loss for neat PLA, 0.1, 0.3, and 0.5 wt% PLA-GR composites are 329, 330, 331, and 332 °C, respectively.

The temperature which corresponds to the maximum rate of weight loss (T_{\max}) is regarded as another significant thermal property for the polymer composite system. The T_{\max} is defined as the peak value that is obtained from the first derivative curve of TGA thermograph. The first derivative curves for PLA and PLA-GR composites are depicted in Fig. 8(b). All the PLA-GR composites and neat PLA show a single peak signifying that the main degradation of these materials proceeded in only one step. It can be noticed that there is an improvement in the T_{\max} value (347 °C) for PLA-GR-0.5 sample in comparison with PLA (345 °C). Enhancement in the thermal stability behavior could be explained by the presence of barrier effect of graphene layers, which limits the emission of the produced degradation gases and transmission of heat, therefore resulting in the improvement in thermal stability of the nanocomposite material.⁵¹

DSC analysis. Non-isothermal cold and melt crystallization behavior of PLA and PLA-GR composites were investigated using DSC analysis. DSC second heating thermographs of neat PLA and PLA composites are shown in Fig. 9. The unimodal endothermic peak (Fig. 9) can be seen at the melting region of PLA ($T_m = 149$ °C), which reveals the α -crystalline form of PLA.^{13,52–54} This unimodal endotherm peak indicates the absence of heterogeneous distribution of crystals and uniform crystal thickness developed after reinforcement of GR due to the melting of stable crystals of PLA formed.^{13,50–53} The addition of GR in the PLA matrix increases the T_m value by 4–5 °C. This is due to the fact that GR reduces the critical nucleus size required for the formation of a thick and stable nucleus in PLA. The current result signifies that the GR acts as a better nucleating agent by enhancing T_m .

In the present study, T_g for PLA composites does not change significantly in comparison with neat PLA. This indicates that the reinforcement of GR does not induce the formation of short chain PLA molecules.^{48,55} The positive effect of reinforced nanofiller on the crystalline properties of PLA can be observed from the Table 3. It is noticed that, all the composite samples

Table 3 DSC results for PLA and PLA-GR composites^a

Sample name	T_g	T_{cc}	T_m	T_{mc}	ΔH_{cc}	ΔH_m	% X_c
PLA	62	110	148	—	16.14	27.2	12
PLA-GR-0.1	63	114	152	100	8.07	25.4	18.5
PLA-GR-0.3	64	113	152.8	101	9.8	27.8	19.2
PLA-GR-0.5	64	110	152.6	101	6.84	23.3	17.5

^a T_g = glass transition temperature, T_{cc} = cold crystallization temperature, T_m = melting temperature, T_{mc} melt crystallization temperature, ΔH_{cc} = enthalpy of cold crystallization, ΔH_m = enthalpy of melting, % X_c = % crystallinity.

display greater level of crystallinity (see Table 3). Improvement in the crystallinity for composite samples can be seen up to 0.3 wt% loadings of GR in comparison with neat PLA. With increase in further loadings of GR, crystallinity (%) slightly decreases. This is probably due to aggregation and poorer dispersion of GR in the PLA matrix. The improved PLA crystallinity with the addition of GR is significant due to the possibility of existence of the greater number of delaminated GR platelets, which can facilitate the PLA crystallization process.

Transparency. The transmission of both visible light and ultraviolet radiation (200–700 nm) is considered as important parameters in designing the packaging materials for specific applications. The photochemical degradation of plastics occurs when exposed to high energy radiation called as UV-B (315–280 nm). Deterioration of food products that are sensitive to visible light takes place in the wavelength region of 400–700 nm.^{56–58} In the wavelength region of 200–700 nm, 72% transmission of light through PLA films is noticed as shown in Fig. 10. This specifies that most of the UV-B and visible radiation pass through PLA films. After reinforcement of GR in the PLA matrix, the transparency of PLA films declines with an increase in the loading of GR (wt%). For the PLA-GR-0.5 composite film, maximum reduction in the transparency is 53% in comparison with neat PLA. This is an advantage provided by GR filler, such that the PLA-GR composite films can find application in the storage of food products containing light sensitive materials such as lipids, flavors, vitamins, and pigments.

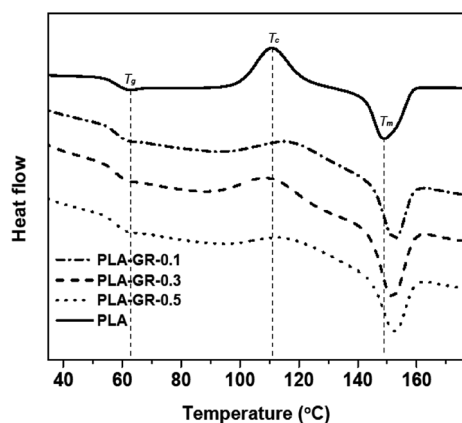


Fig. 9 DSC second heating thermographs for PLA and PLA-GR composites at a heating rate of 5 °C min⁻¹.

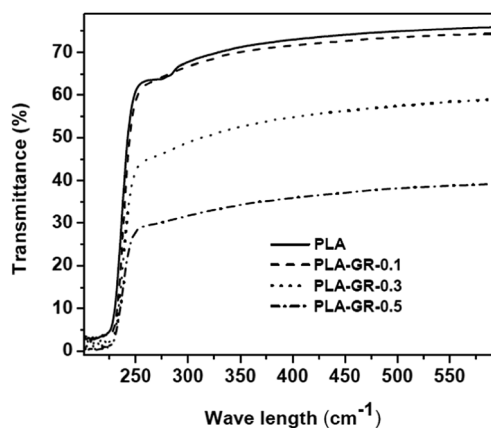


Fig. 10 Transparency measurements for PLA and PLA-GR composites.

Mechanical properties. The tensile strength and elongation-at-break properties of PLA and PLA-GR composites are presented in Fig. 11. The tensile strength of the PLA-GR composites is found to be higher for 0.1 wt% loading (40 MPa) of GR when compared with neat PLA (32 MPa). The PLA-GR-0.1 composite exhibits the highest tensile strength of 40 MPa compared to PLA-GR-0.3 (37 MPa) and PLA-GR-0.5 (31 MPa). It reveals that the stress applied is transferred from PLA matrix to the GR. The gradual roll-off in the tensile strength values for further loadings explicates that addition as well as dispersion of GR in the PLA matrix are the dominant factors to enhance the mechanical properties. Therefore, it is clear that noticeable aggregation and the quality of dispersion become inferior at higher loading of GR (>0.1%). As a result, a slight decrease in the tensile strength is observed for the PLA composites. The elongation-at-break value obtained for 0.1 wt% of GR content is 53%, which is higher than that of neat PLA. This implies that the ductility of PLA is effectively improved with the incorporation of GR. GR acts as a bridge to prolong the fracture process of PLA composites and thereby reduces the sudden risk of failure. At further loadings of GR (0.3 and 0.5 wt%), elongation-at-break values display the downturn of around ~41% and 45%, respectively. This is because, defects induced by the agglomeration of GR sheets account for greater brittleness of the PLA matrix. However, GR reinforced in the PLA matrix demonstrates a positive impact on the tensile strength as well as elongation at break properties at lower GR loadings (0.1 wt%) in comparison with the PLA-EG composites produced by Marius *et al.*³³ In their study, it was reported that the addition of EG in the PLA matrix showed a negative impact on the above properties at all the

loadings (wt%) of EG due to the aggregation of graphene stacks. Hence, it is clear that the sonication process utilized in the present study to separate the graphene plays an effective role in enhancing the strength and ductility of the PLA composites.

Film permeability. For semi-crystalline polymers, like PLA, oxygen barrier characteristics are directed by permeation and diffusion of oxygen molecules through the amorphous phase of polymer film. To enhance the barrier properties of PLA, inclusion of impermeable barriers that reduces the gas permeation by creating the tortuous pathway is important. In the current investigation, the influence of graphene on inhibition of oxygen transport through PLA films is examined at various temperatures (25–45 °C) and the results are presented in Table 4. The permeation of oxygen is reduced by 22% (25 °C) after incorporating 0.1 wt% GR in the PLA matrix. This is attributed to the tortuous path effect generated by the exfoliated GR nanosheets, which hinders the oxygen transport in the PLA film. However, at higher loadings of GR, further improvement in oxygen permeation is not observed. This may be caused by the formation of GR aggregates at higher loadings. For both PLA and PLA-GR composite systems, oxygen permeation increases with increasing temperature, due to the fast diffusion of gas molecules through the PLA matrix at higher temperature. At 45 °C, the oxygen permeation for PLA composite containing 0.1 wt% GR is reduced about 40%. This indicates that the addition of GR acts as an effective impermeable barrier for oxygen transport even at higher temperature.

Thermal degradation kinetics of PLA-GR composites. Kinetic studies of degradation process are performed for better understanding of the thermal degradation behavior of PLA and PLA-GR composites. The kinetics of thermal degradation of GR based biopolymer composites can be expressed by the following typical kinetic equation

$$\frac{d\alpha}{dt} = kf(\alpha) \quad (4)$$

where, α is the conversion degree or the fraction decomposed [$\alpha = (w_0 - w_t)/w_0 - w_f$], w_0 , w_t , and w_f are the initial, time t , and final weights of the polymer], $\frac{d\alpha}{dt}$ is the rate of conversion, k is the temperature-degradation rate constant, and $f(\alpha)$ is the differential expression of a kinetic model function, which depends on the particular degradation mechanism.^{59–61}

The temperature dependent degradation rate constant (k) can be expressed in terms of the Arrhenius equation as follows:

$$k = A \exp\left(\frac{-E_a}{RT}\right) \quad (5)$$

where, A is the pre-exponential factor (s^{-1}), E_a is the apparent activation energy of the degradation reaction ($kJ\ mol^{-1}$), R is the universal gas constant ($8.314\ J\ mol^{-1}\ K^{-1}$), and T is the absolute temperature (K). By substituting k from eqn (5) in to (4), a general expression for the kinetic process under isothermal conditions can be derived and expressed as

$$\frac{d\alpha}{dt} = A \exp\left(\frac{-E_a}{RT}\right) f(\alpha) \quad (6)$$

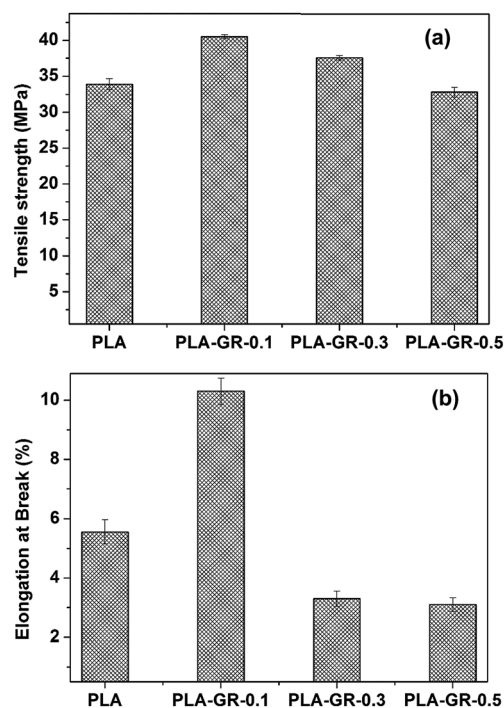


Fig. 11 (a) Tensile strength and (b) elongation-at-break for PLA and PLA-GR nanocomposites.

Table 4 Effect of graphene content on oxygen permeability (OP) of PLA-GR composite films

Sample name	Temperature (°C)	Oxygen permeability (cm ³ per mm/m ² per day per atm)	% Reduction in oxygen permeability
PLA	25	23	—
	35	33	—
	45	51	—
PLA-GR-0.1	25	18	22
	35	22	33
	45	31	40
PLA-GR-0.3	25	20	13
	35	23	30
	45	35	32
PLA-GR-0.5	25	22	4
	35	30	9
	45	40	14

In the present study, the thermal degradation kinetic study of PLA-GR composites is carried out under non-isothermal conditions, where samples are heated with a constant heating rate, $\beta = \frac{dT}{dt}$. Hence, eqn (6) is transformed into an equation which describes the degradation reaction rate as a function of temperature and then expressed as follows:

$$\left(\frac{d\alpha}{dT}\right) = \frac{A}{\beta} \exp\left(\frac{-E_a}{RT}\right) f(\alpha) \quad (7)$$

Eqn (6) and (7) are the basic expressions of analytical procedures for the calculation of kinetic triplets from the TGA data.^{13,60–62}

Taking integration on both sides and rearranging

$$g(\alpha) = \int_0^\alpha \frac{d\alpha}{f(\alpha)} = \frac{A}{\beta} \int_0^T e^{\frac{-E_a}{RT}} dT \quad (8)$$

where, $g(\alpha)$ is the integral function of conversion degree, α . The process of polymer degradation mainly obeys sigmoidal or deceleration functions.

Coats-Redfern method. Using eqn (8) and putting $f(\alpha) = (1 - \alpha)^n$ and $x = E_a/RT$ and rearranging, we get:

$$g(\alpha) = \frac{ART^2}{\beta E_a} \left(1 - \frac{2RT}{E_a}\right) \exp\left(\frac{E_a}{RT}\right) \quad (9)$$

$g(\alpha)$ can be written in different ways for different n values.

$$\text{When } n = 1, g(\alpha) = -\ln(1 - \alpha) \quad (10)$$

$$\text{When } n \neq 1, g(\alpha) = \frac{1}{n-1} \left[(1 - \alpha)^{1-n} - 1\right] \quad (11)$$

The combination of eqn (10) and (11) and by rearrangement, we get:

$$n = 1, \ln\left(\frac{-\ln(1 - \alpha)}{T^2}\right) = \ln\left[\frac{AR}{\beta E_a} \left(1 - \frac{2RT}{E_a}\right)\right] - \frac{E_a}{RT} \quad (12a)$$

$$n \neq 1, \ln\left(\frac{1 - (1 - \alpha)^{1-n}}{(1 - n)T^2}\right) = \ln\left[\frac{AR}{\beta E_a} \left(1 - \frac{2RT}{E_a}\right)\right] - \frac{E_a}{RT} \quad (12b)$$

Plotting the left hand side term *versus* $-1/T$ gives the straight line and activation energy is obtained from the slope of the straight line. The value of the pre-exponential factor, A is obtained from intercept of the straight line, by considering the expression $\left(1 - \frac{2RT}{E_a}\right)$ inside the parenthesis as 1.^{63,64} Analysis is done using only single heating data, which is different from other kinetic models where multiple heating data are required for analysis.

The Coats-Redfern method requires TG data with only one heating rate to calculate kinetic parameters such as activation energy (E_a), reaction order (n) and pre-exponential factor (A).⁵⁹ In this study, TGA data of PLA composite samples with different GR loadings are taken at a single heating rate (10 °C min⁻¹). For this method, a reaction order “ n ” is assumed and the assumed value is substituted in eqn (12a) and (12b). The plot of the left hand side of the eqn (12a) and (12b) *versus* $-1/T$ is fitted to calculate the R^2 values. This process is repeated until the best R^2 value is obtained. Fig. 12 shows the linear fitted graph for neat PLA and PLA-GR composites for various “ n ” values. The calculated reaction order at the best R^2 value is considered as the reaction order for that sample. Then the activation energy and the pre-exponential factor are obtained from the slope and intercept of the fitted straight line. The activation energy of neat PLA and PLA-GR composite samples containing 0.1, 0.3 and 0.5 wt% GR is 125, 129, 137, and 146 kJ mol⁻¹, respectively. This clearly indicates that GR acts as an effective nucleating agent and enhances the thermal properties of PLA matrix.

Criado method. The mechanism of thermal degradation of PLA-GR composites at a particular heating rate is predicted using Criado method.⁶⁵ The reaction mechanism is determined with the help of activation energy, pre-exponential factor and the apparent order of the reaction calculated using the Coats-Redfern method. Criado equation is given by

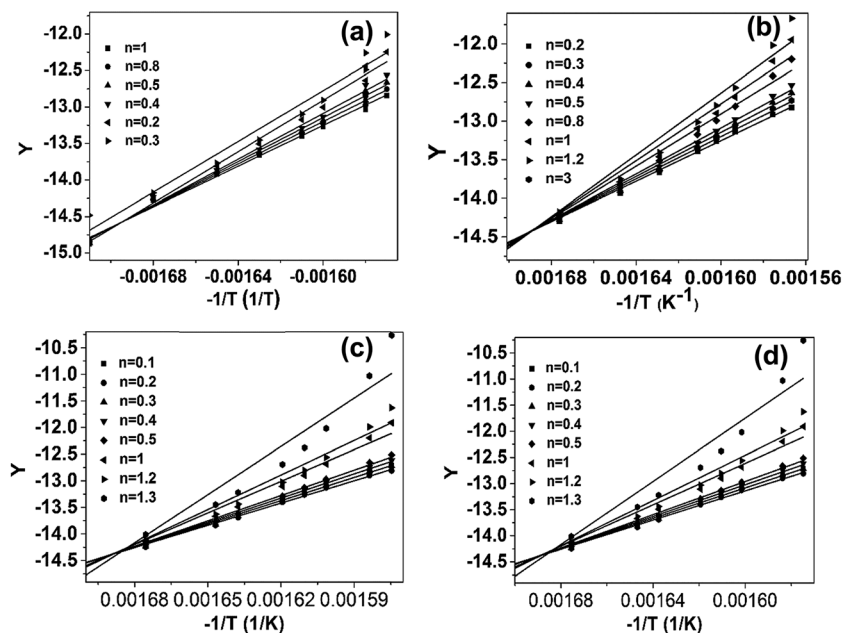


Fig. 12 Determination of kinetic parameters by plots of the left part in eqn (12) against $-1/T$ using Coats-Redfern method: (a) neat PLA, (b) PLA-GR-0.1, (c) PLA-GR-0.3 and (d) PLA-GR-0.5.

$$Z(\alpha) = \frac{d\alpha}{\beta} \pi(x) T \quad (13)$$

where, $x = \frac{E_a}{RT}$ and $\pi(x)$ is an expression resulted by integration against temperature, that cannot be articulated using simple analysis formula. A relationship between $\pi(x)$ and $P(x)$ is reported elsewhere⁶⁶ and is given as follows

$$\pi(x) = x e^x P(x) \quad (14)$$

where, $P(x)$ is expressed as:

$$P(x) = \frac{e^{-x}}{x} \frac{x^3 + 18x^2 + 86x + 96}{x^4 + 20x^3 + 120x^2 + 240x + 120} \quad (15)$$

Combining eqn (13)–(15), the following relationship can be obtained

$$Z(\alpha) = f(a)g(\alpha) \quad (16)$$

Combining eqn (7) with (16) provides the following relationship

$$Z(\alpha) = \frac{\beta}{A} g(\alpha) \frac{d\alpha}{dT} \exp\left(\frac{E_a}{RT}\right) \quad (17)$$

From the eqn (13) and (14), the following relationship is obtained

Table 5 Expression of $g(\alpha)$ for the most frequently used reaction mechanism of solid state processes

Mechanism	$g(\alpha)$	Solid state process
Sigmoidal function		
A_2	$[-\ln(1 - \alpha)]^{1/2}$	Nucleation and growth Avrami eqn (1)
A_3	$[-\ln(1 - \alpha)]^{1/3}$	Nucleation and growth Avrami eqn (2)
A_4	$[-\ln(1 - \alpha)]^{1/4}$	Nucleation and growth Avrami eqn (3)
Deceleration function		
R_2	$[-\ln(1 - \alpha)]^{1/2}$	Phase boundary controlled reaction: contraction area
R_3	$[-\ln(1 - \alpha)]^{1/3}$	Phase boundary controlled reaction: contraction area
D_1	α^2	One-D diffusion
D_2	$(1 - \alpha) \ln(1 - \alpha) + \alpha$	Two-D diffusion
D_3	$[1 - (1 - \alpha)^{1/3}]^2$	Three-D diffusion: Jander equation
D_4	$-\ln(1 - \alpha)$	Three-D diffusion: Ginstling-Brounshtein equation
F_1	$-\ln(1 - \alpha)$	Random nucleation having one nucleus on individual particle
F_2	$1/(1 - \alpha)$	Random nucleation having two nucleus on individual particle
F_3	$1/(1 - \alpha)^2$	Random nucleation having two nucleus on individual particle

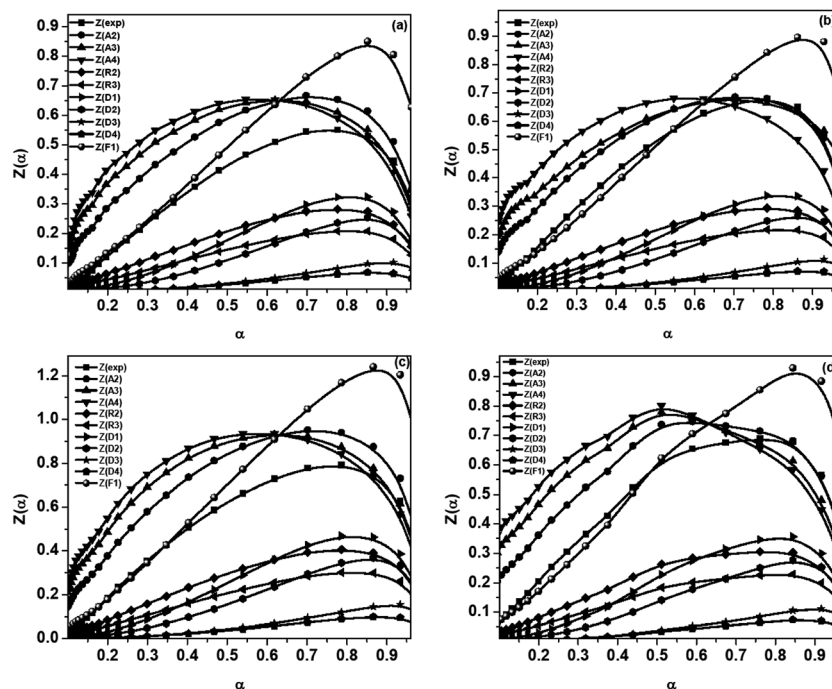


Fig. 13 Determination of the thermal degradation reaction mechanism by plots of $Z(\alpha)$ versus α using Criado method. (a) Neat PLA, (b) PLA-GR-0.1, (c) PLA-GR-0.3 and (d) PLA-GR-0.5.

$$Z(\alpha) = \frac{d\alpha}{dT} \frac{E_a}{R} \exp\left(\frac{E_a}{RT}\right) P(x) \quad (18)$$

The master $Z(\alpha) - \alpha$ curve of the different reaction mechanisms given in Table 5 is plotted using eqn (17), and the $Z(\alpha) - \alpha$ experimental curve is plotted using eqn (18).⁶³ Thereafter, the master $Z(\alpha) - \alpha$ curve has been compared with the experimental $Z(\alpha) - \alpha$ curve for predicting the reaction mechanism of the thermal degradation process of PLA-GR composites.

The kinetic parameters obtained for $10^\circ\text{C min}^{-1}$ heating rate using the Coats-Redfern method are substituted in the eqn (17) and (18). Fig. 13(a-d) illustrates the $Z(\alpha) - \alpha$ master and experimental curves for neat PLA and PLA-GR composites samples with 0.1, 0.3 and 0.5 wt% GR. It can be perceived that the experimental curves of neat PLA (Fig. 13(a)) overlaps with the master curves of $Z(F_1)$, suggesting that the thermal degradation process of neat PLA follows the F_1 reaction mechanism. This indicates that random nucleation is the rate controlling step associated with the nucleation process at lower α values (0.1–0.55). After adding GR, at the initial phase, the thermal degradation process proceeds via F_1 reaction mechanism for all PLA composite samples. With further progress in the degradation reaction, the system, however, slowly changes towards A_3 mechanism (which involves both nucleation and growth) at higher α value (0.7–0.95). This might be possibly due to the shift in the thermal degradation mechanism at higher temperature conditions.

Conclusions

In the current article, expandable graphite (EG) is subjected to thermal shock at different temperatures ranging from 200 – 1000°C . The optimum condition for thermal exfoliation is determined as 750°C . The HRTEM image pictorialized after sonication and SAED pattern display a monolayer GR. No diffraction peak corresponding to graphene is observed from the XRD patterns of PLA-GR composites prepared with 30 min sonication due to exfoliation of GR in the PLA matrix. The TGA analysis reveals that the thermal stability of PLA-GR-0.5 composites improves about 6°C when 10% weight loss is taken as a point of comparison. Improvement in the thermal stability can also be corroborated from the enhancement in the activation energy exhibited by PLA composites. The presence of GR greatly improves melting temperature of about 4°C as well as the crystallization ability of PLA during the non-isothermal crystallization processes. This indicates that GR acts as an effective nucleating agent in enhancing the crystallization behavior of PLA. In the UV-B and visible radiation region (200 – 700 nm), 53% reduction in the transparency for PLA films is observed after reinforcement of GR. The tensile strength of PLA-GR composites is found to be maximum (40 MPa) for 0.1 wt% loading of GR in comparison with neat PLA, which is an indication of good adhesion between PLA and the filler.

Acknowledgements

Authors are thankful to the Central Instrument Facility (CIF), IIT Guwahati for helping to perform TEM, FE-SEM and BET

analysis. Authors sincerely thank the Department of Chemicals & Petrochemicals, Ministry of Chemicals and Fertilizers, Government of India - funded Center of Excellence for Sustainable Polymers at IIT Guwahati for research facilities to perform this current research work. XRD used in this work was financially supported by a FIST grant (SR/FST/ETII-028/2010) from Department of Science and Technology (DST), Government of India.

References

- 1 P. Pan, Z. Liang, A. Cao and Y. Inoue, *ACS Appl. Mater. Interfaces*, 2009, **1**, 402–411.
- 2 Y. Inoue and N. Yoshie, *Prog. Polym. Sci.*, 1992, **17**, 571–610.
- 3 M. A. Paul, M. Alexandre, P. H. Degee, C. Henrist, A. Rulmont and P. H. Dubois, *Polymer*, 2003, **44**, 443–450.
- 4 M. Pluta, *Polymer*, 2004, **45**, 8239–8251.
- 5 H. Zhao, Z. Cui, X. Wang, L. Turng and X. Peng, *Composites, Part B*, 2013, **51**, 79–91.
- 6 H. Chena, M. Pydab and P. Cebe, *Thermochim. Acta*, 2009, **492**, 61–66.
- 7 M. Murariu, A. Da Silva Ferreira, P. H. Degee, M. Alexandre and P. H. Dubois, *Polymer*, 2007, **48**, 2613–2618.
- 8 N. C. Bleach, S. N. Nazhat, K. E. Tanner, M. Kellomaki and P. Tormala, *Biomaterials*, 2002, **23**, 1579–1585.
- 9 M. Murariu, L. Bonnaud, P. Yoann, G. Fontaine, S. Bourbigot and P. H. Dubois, *Polym. Degrad. Stab.*, 2010, **95**, 374–381.
- 10 S. Bourbigot, G. Fontaine, S. Duquesne and R. Delobel, *Int. J. Nanotechnol.*, 2008, **5**, 683–692.
- 11 A. L. Goffin, E. Duquesne, S. Moins, M. Alexandre and P. H. Dubois, *Eur. Polym. J.*, 2007, **43**, 4103–4113.
- 12 T. Villmow, P. Potschke, S. Pegel, L. Haussler and B. Kretschmar, *Polymer*, 2008, **49**, 3500–3509.
- 13 R. Valapa, G. Pugazhenthii and V. Katiyar, *Int. J. Biol. Macromol.*, 2014, **65**, 275–283.
- 14 F. Hussain, M. Hojjati, M. Okamoto and R. E. Gorga, *J. Compos. Mater.*, 2006, **40**, 1511–1575.
- 15 Q. Bao, H. Zhang, J. Yang, S. Wang, D. Y. Tang, R. Jose, S. Ramakrishna, C. T. Lim and K. P. Loh, *Adv. Funct. Mater.*, 2009, **20**, 782–791.
- 16 Y. Zhu, S. Murali, W. Cai, X. Li, J. W. Suk, J. R. Potts and R. S. Ruoff, *Adv. Mater.*, 2010, **22**, 3906–3924.
- 17 O. C. Compton and S. T. Nguyen, *Small*, 2010, **6**, 711–723.
- 18 K. J. Huang, D. J. Niu, J. Y. Sun, C. H. Han, Z. W. Wu, Y. L. Li and X. Q. Xiong, *Colloids Surf., B*, 2010, **82**, 543–549.
- 19 P. K. Ang, M. Jaiswal, C. H. Lim, Y. Wang, J. Sankaran, A. Li, C. T. Lim, T. Wohland, O. Barbaros and K. P. Loh, *ACS Nano*, 2010, **4**, 7387–7394.
- 20 S. R. Ryoo, Y. K. Kim, M. H. Kim and D. H. Min, *ACS Nano*, 2010, **4**, 6587–6598.
- 21 M. S. Dresselhaus and G. Dresselhaus, *Adv. Phys.*, 2002, **51**, 1–186.
- 22 Z. Spitalsky, M. Danko and J. Mosnacek, *Curr. Org. Chem.*, 2011, **15**, 1133–1150.
- 23 A. Celzard, J. F. Mareche and G. Furdin, *Prog. Mater. Sci.*, 2005, **50**, 93–179.
- 24 S. Stankovich, D. A. Dikin, G. H. B. Dommett, K. M. Kohlhaas, E. J. Zimney, E. A. Stach, R. D. Piner, S. T. Nguyen and R. S. Ruoff, *Nature*, 2006, **442**, 282–286.
- 25 Y. Cao, J. Feng and P. Wu, *Carbon*, 2010, **48**, 3834–3839.
- 26 L. S. Viculis, J. J. Mack, O. M. Mayer, H. T. Hahn and R. B. Kaner, *J. Mater. Chem.*, 2005, **15**, 974–978.
- 27 K. E. Carr, *Carbon*, 1970, **8**, 155–158.
- 28 G. Chen, D. Wu, W. Weng and C. Wu, *Carbon*, 2003, **41**, 619–621.
- 29 Y. X. Pan, Z. Z. Yu, Y. C. Ou and G. H. Hu, *J. Polym. Sci., Part B: Polym. Phys.*, 2000, **38**, 1626–1633.
- 30 K. Kalaitzidou, H. Fukushima and L. T. Drzal, *Compos. Sci. Technol.*, 2007, **67**, 2045–2051.
- 31 Y. W. Cao, J. C. Feng and P. Y. Wu, *Carbon*, 2010, **48**, 1683–1685.
- 32 S. Niyogi, E. Bekyarova, M. E. Itkis, J. L. McWilliams, M. A. Hamon and R. C. Haddon, *J. Am. Chem. Soc.*, 2006, **128**, 7720–7721.
- 33 M. Murariu, A. L. Dechief, L. Bonnaud, Y. Paint, A. Gallos, G. Fontaine, S. Bourbigot and P. Dubois, *Polym. Degrad. Stab.*, 2010, **95**, 889–900.
- 34 D. Garlotta, *J. Polym. Environ.*, 2001, **9**, 63–84.
- 35 H. Xiang, K. Zhang, G. Ji, J. Y. Lee, C. Zou, X. Chen and J. Wu, *Carbon*, 2011, **49**, 1787–1796.
- 36 A. Yasmin, J. J. Luo and I. M. Daniel, *Compos. Sci. Technol.*, 2006, **66**, 1179–1189.
- 37 K. S. W. Singh, D. H. Everett, R. A. W. Haul, L. Moscou, R. A. Pierotti, J. Rouquerol and T. Siemieniowska, *Pure Appl. Chem.*, 1985, **57**, 603–619.
- 38 S. Stankovich, D. A. Dikin, R. D. Piiner, K. A. Kohlhaas, A. Kleinhammes, Y. Jai, Y. Wu, S. T. Nguyen and R. S. Rouf, *Carbon*, 2007, **45**, 1558–1565.
- 39 I. M. Afanasov, O. N. Shornikova, D. A. Kirilenko, I. I. Vlasov, L. Zhang, J. Verbeeck, V. V. Avdeev and G. V. Tendeloo, *Carbon*, 2010, **48**, 1862–1865.
- 40 K. Fukushima, M. Murariu, G. Camino and P. Dubois, *Polym. Degrad. Stab.*, 2010, **95**, 1063–1076.
- 41 J. M. Mcallister, J. L. Li, D. H. Admson, H. C. Schniepp, A. A. Abdala, J. Liu, M. H. Alonso, D. L. Milius, C. Reoberto, R. K. Prudhomme and I. A. Aksay, *Chem. Mater.*, 2007, **19**, 4396–4404.
- 42 P. Cui, J. Lee, E. Hwang and H. Lee, *Chem. Commun.*, 2011, **47**, 12370–12372.
- 43 V. Krikorian and D. J. Pochan, *Chem. Mater.*, 2003, **15**, 4317–4324.
- 44 E. Narimissa, R. Gupta, M. Bhaskaran and S. Sriram, *Polym. Degrad. Stab.*, 2012, **97**, 829–832.
- 45 Y. Fan, H. Nishida, Y. Shirai, Y. Tokiwa and T. Endo, *Polym. Degrad. Stab.*, 2004, **86**, 197–208.
- 46 Y. Fan, H. Nishida, Y. Shirai and T. Endo, *Polym. Degrad. Stab.*, 2004, **84**, 143–149.
- 47 V. Taubner and R. Shishoo, *J. Appl. Polym. Sci.*, 2001, **79**, 2128–2135.
- 48 Y. Wang and J. F. Mano, *Eur. Polym. J.*, 2005, **41**, 2335–2342.
- 49 Y. Wang, B. Steinhoff, C. Brinkmann and I. Alig, *Polymer*, 2008, **49**, 1257–1265.

- 50 H. Yu, N. Huang, C. Wang and Z. Tang, *J. Appl. Polym. Sci.*, 2003, **88**, 2557–2562.
- 51 X. Wang, W. Xing, P. Zhang, L. Song, H. Yang and Y. Hu, *Compos. Sci. Technol.*, 2012, **72**, 737–743.
- 52 F. Peng, M. T. Shaw, J. R. Olson and M. Wei, *J. Phys. Chem. C*, 2011, **115**, 15743–15751.
- 53 D. Sawai, K. Takahashi, A. Sasashige, T. Kanamoto and S. H. Hyon, *Macromolecules*, 2003, **36**, 3601–3605.
- 54 W. Hoogsteen, A. R. Postema, A. J. Pennings and G. T. Brinke, *Macromolecules*, 1990, **23**, 634–642.
- 55 L. Liu, T. Z. Jin, D. R. Coffin and K. B. Hicks, *J. Agric. Food Chem.*, 2009, **57**, 8392–8398.
- 56 H. Chen, W. Zhang, X. Du, J. Yang, N. Zhang, T. Huang and Y. Wang, *Thermochim. Acta*, 2013, **566**, 57–70.
- 57 R. Auras, B. Harte and S. Selke, *Macromol. Biosci.*, 2004, **4**, 835–864.
- 58 J. J. Hernandez, M. C. Garcia-Gutierrez, A. Nogales, D. R. Rueda, M. Kwiatkowska, A. Szymczyk, Z. Roslaneic, A. Concheso, I. Guinea and T. A. Ezquerro, *Compos. Sci. Technol.*, 2009, **69**, 1867–1872.
- 59 I. Armentano, N. Bitinis, E. Fortunati, S. Mattioli, N. Rescignano, R. Verdejo, M. A. Lopez-Manchado and J. M. Kenny, *Prog. Polym. Sci.*, 2013, **38**, 1720–1747.
- 60 D. F. Wu, L. Wu, L. F. Wu and M. Zhang, *Polym. Degrad. Stab.*, 2006, **91**, 3149–3155.
- 61 A. Khawan and D. R. Flanagan, *J. Phys. Chem. B*, 2006, **110**, 17315–17328.
- 62 E. IYuzay, R. Auras, H. Valdez and S. Selke, *Polym. Degrad. Stab.*, 2010, **95**, 1769–1777.
- 63 S. V. Krishna and G. Pugazhenth, *J. Appl. Polym. Sci.*, 2011, **120**, 1322–1336.
- 64 M. Poletto, A. J. Zattera and R. M. C. Santana, *Bioresour. Technol.*, 2012, **126**, 7–12.
- 65 J. M. Criado, J. Malek and A. Ortega, *Thermochim. Acta*, 1989, **147**, 377–385.
- 66 J. H. Flynn, *Thermochim. Acta*, 1997, **300**, 83–92.