



Cite this: *J. Mater. Chem. B*, 2015, **3**, 3604

Switchable dispersivity and molecular-trapping performance of mesostructured CaCO_3 -thermosensitive polymer composite microspheres

Atsuharu Inoue,^a Hitoshi Tamagawa,^a Yuya Oaki,^a Sadahito Aoshima^b and Hiroaki Imai^{*a}

Monodispersed thermosensitive microspheres were synthesized by the combination of poly(*N*-isopropylacrylamide) (PNIPAAm) and a mesostructured framework consisting of vaterite CaCO_3 nanocrystals ~ 20 nm in diameter. The switchable dispersivity in water and organic media was provided to the rigid porous framework by the soft shell of the thermosensitive organic component. The microspheres were shuttlecocked between water and hydrophobic organic media by a swing in temperature across the lower critical solution temperature (LCST). The composite microspheres performed as an active carrier of organic molecules due to their switchable property. Hydrophobic molecules were captured by the microspheres dispersed in an organic medium above LCST and were then delivered and released to another organic phase through a water phase by a swing in temperature.

Received 17th February 2015,
Accepted 24th March 2015

DOI: 10.1039/c5tb00342c

www.rsc.org/MaterialsB

Introduction

Biomaterials are known as inorganic-organic composites that are elaborately organized from nanoscopic to macroscopic scales.^{1–9} In recent years, most CaCO_3 -based biomaterials were revealed to have a hierarchical architecture composed of nanometric crystals.^{10–12} These specific nanostructures are categorized as a kind of meso-crystal, *i.e.*, mesostructured crystals consisting of oriented nanoscale units that are covered with organic molecules. The architectures and formation processes of biomaterials have provided considerable inspiration in the field of materials chemistry, leading to new fabrication techniques and the development of novel functionalities.¹³ Recently, well-defined microspheres of CaCO_3 nanoparticles were produced in various solution systems.^{14–18} In our previous work,¹⁹ monodispersed microspheres having an oriented nanocrystal mosaic interior were obtained through the crystal growth of CaCO_3 with polystyrene sulfonate (PSS) under specific conditions. The CaCO_3 -based mesocrystal is a potential host material because various guest molecules can be introduced in the interspatial organic domains between the oriented nanocrystals.^{20–23} From the standpoint of the exploration of their function, however, the CaCO_3 -based mesocrystals have hardly been studied for practical applications.

Poly(*N*-isopropylacrylamide) (PNIPAAm) exhibits a lower critical solution temperature (LCST) transition from 32 to 34 °C.²⁴ The

polymer is hydrophilic and soluble in water below LCST but becomes hydrophobic and forms a macroscopic coacervate phase above that temperature due to the fluctuation of hydrophobic interactions and hydrogen bonding.²⁵ The introduction of the polymer onto the nanoparticles of metals and other kinds of polymers provides their responsivity to temperature.^{26,27} For example, block copolymers including PNIPAAm formed a micelle and were applied as a drug delivery system (DDS).²⁸ Gold²⁹ and mesoporous silica^{30,31} nanoparticle composites with PNIPAAm are also applied as a DDS. Hydrogel composites containing PNIPAAm colloidal crystals were utilized as a photonic crystal.³²

In the present study, we prepared the monodispersed thermosensitive microspheres of mesostructured CaCO_3 that was covered with a shell of PNIPAAm. The original polymer (PSS) covering the specific crystalline structure of oriented vaterite CaCO_3 nanoparticles was replaced by the functional molecule. The influence of temperature on the dispersivity in various media was investigated. Moreover, the release and retention abilities of the microspheres for a hydrophobic molecule were monitored according to the swing in temperature. The potential of the CaCO_3 -based thermosensitive microspheres as an active carrier is discussed on the basis of their switchable dispersivity and molecular-trapping performance by the tuning of temperature.

Experimental

We prepared mesostructured CaCO_3 crystals by using a simple mixing method of two solutions at room temperature.¹⁹ Typically, 128 cm³ of 1.0 mol dm^{−3} CaCl_2 solution was added to 4.0 dm³ of

^a Department of Applied Chemistry, Faculty of Science and Technology, Keio University, 3-14-1 Hiyoshi, Kohoku-ku, Yokohama 223-8522, Japan. E-mail: hiroaki@aplc.keio.ac.jp

^b Department of Macromolecular Science, Graduate School of Science, Osaka University, 1-1 Machikaneyama-cho, Toyonaka, Osaka 560-0043, Japan



16 mmol dm⁻³ sodium carbonate (Na₂CO₃, Junsei Chemical 99.8%) solution containing 1.0 g dm⁻³ PSS (Aldrich, *M*^w: 70 000). After mixing, the solution was stirred for 60 s, and then left for 24 h. The organic components included in the products were extracted by immersion in a 5 wt% NaClO aqueous solution for 48 h. The resultant samples were then washed extensively with purified water. *N*-Isopropylacrylamide (NIPAAm) as a monomer and methylene-bisacrylamide (MBA) as a crosslinker were introduced into the nanopores of the microspheres by impregnation of the mixture. The polymerization was performed in hexane containing 0.01 g of 2,2'-dimethoxy-2-phenylacetophenone (BDK) as an initiator under UV illumination for 3 h using Ushio OPM2-502XQ (3.8 W). Finally, we obtained the composite microspheres 2–3 μm in diameter through classification by dispersivity in water and a subsequent freeze-drying process.

The dispersivity of 5 mg microspheres in 15 cm³ water was evaluated by changing the temperature between 25 and 60 or 90 °C. We observed the turbidity in a test tube and aggregation behavior on a glass slide under an optical microscope. A toluene–water–nitrobenzene system was used to examine the dispersivity of the composite microspheres. We put 15 dm³ nitrobenzene, 15 dm³ water containing 7 mg of the CaCO₃–PNIPAAm composite powder, and 15 dm³ toluene into a glass vessel in order. The three-phase system was stirred at 20 or 90 °C for 72 h with ultrasonic agitation. The fixing ability of the microspheres was studied using a hydrophobic surface of a glass slide prepared by dipping of a toluene solution of 1 wt% dodecyltrichlorosilane. Alkyl chains were formed on the glass surface after subsequent drying.

Copper phthalocyanine (CuPh, a blue hydrophobic pigment) was introduced into the CaCO₃–PNIPAAm composites by the following process. The composite powder (10 mg) was dispersed in 20 dm³ water at room temperature. Toluene (20 dm³) containing 0.2 mmol dm⁻³ of CuPh was poured on the aqueous dispersion. After the vessel containing the two-phase system was stirred at 90 °C for 72 h with ultrasonic agitation once in a while, the composite particles were transferred into the organic phase. By stirring at room temperature for 72 h with ultrasonic agitation once in a while, the pigment-containing composite particles were redispersed in water. The pigment was released from the composites in a fresh organic phase at 90 °C. The concentration of the pigment was monitored from the absorption spectra in the ultraviolet-visible region using a Jasco V-560. We also examined the transport of CuPh using a toluene–water–toluene system in a U-tube. The composite microspheres were shuttlecocked between the organic and water phases by a swing in temperature with ultrasonic agitation.

The morphology of the products was characterized using a field-emission scanning electron microscope (FESEM, Hitachi S-4700) and a field-emission transmission electron microscope (FETEM, FEI Tecnai F20). Optical images were taken using Keyence VHX 1000. The X-ray diffraction (XRD) patterns were recorded using Rigaku MiniFlex II with Cu Kα radiation. The pore-size distribution was evaluated from nitrogen adsorption–desorption isotherms obtained using Miromeritics Tristar 3000. The weight of the organic components was measured by thermogravimetry (TG) using Seiko Instruments TG/DTA 7200. The kind

of organic components was measured by Fourier transform infrared spectroscopy (FT-IR) using Jasco FT-IR 4200.

Results and discussion

As shown in Fig. 1a, well-defined microspheres *ca.* 2.5 μm in diameter were produced in 24 h after the mixing of a calcium solution and a carbonate solution containing 1.0 g dm⁻³ PSS. In the SEM images of the cross section and surface of the CaCO₃–PSS composite microspheres (Fig. 1b and c), the microspheres consisted of small particles with a diameter of *ca.* 20 nm, as illustrated in Fig. 1d. According to the XRD patterns (Fig. 2a), the microspheres were assigned to be pure vaterite. The PSS-mediated vaterite spheres were stable for a long time in water and an ambient atmosphere. The crystalline grains composed of the microspheres were clearly observed after the decomposition of PSS by using a NaClO solution (Fig. 1e–h). The pore volume as an interparticular space in the microspheres increased with the removal of the organic component after the treatment.

After the polymerization of NIPAAm, the interparticular space was filled with the organic phase (Fig. 1i–l). After the dissolution of CaCO₃ with an HCl solution, the *ca.* 300 nm thick shell of the polymer was clearly observed (Fig. 1m–o). The nanostructure was found on the surface of the polymer shell. Fig. 2b shows the FT-IR spectra of the CaCO₃–polymer composite microspheres before and after treatment. We observed typical absorption bands of the vaterite phase at 744 (ν₂ mode of CO₃²⁻) and 877 cm⁻¹ (ν₄ mode of CO₃²⁻) for all the samples. The CaCO₃–PSS composites have strong peaks at 1130 and 1210 cm⁻¹ due to SO₃⁻ and 1,4-substituted benzene of PSS, respectively. These absorption signals decreased with the NaClO treatment. The presence of amide II group absorption at 1655 cm⁻¹ indicates the formation of

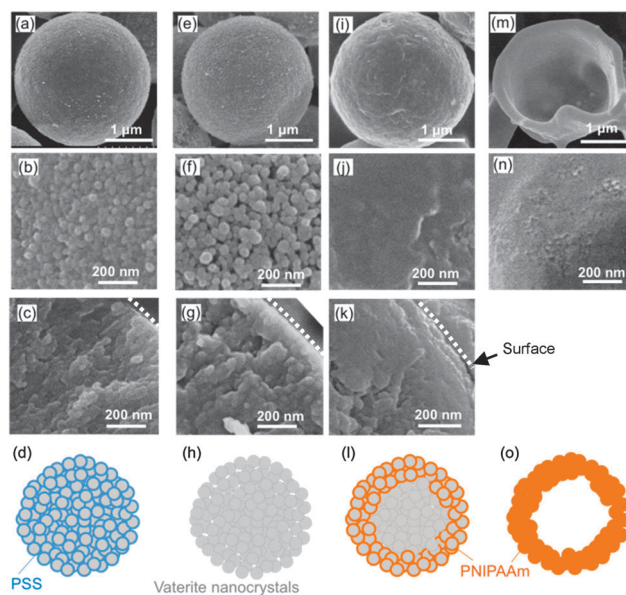


Fig. 1 SEM images and schematic illustrations of CaCO₃–PSS (a–d), CaCO₃–PSS after the NaClO treatment (e–h), CaCO₃–PNIPAAm (i–l), and CaCO₃–PNIPAAm after the HCl treatment (m–o).



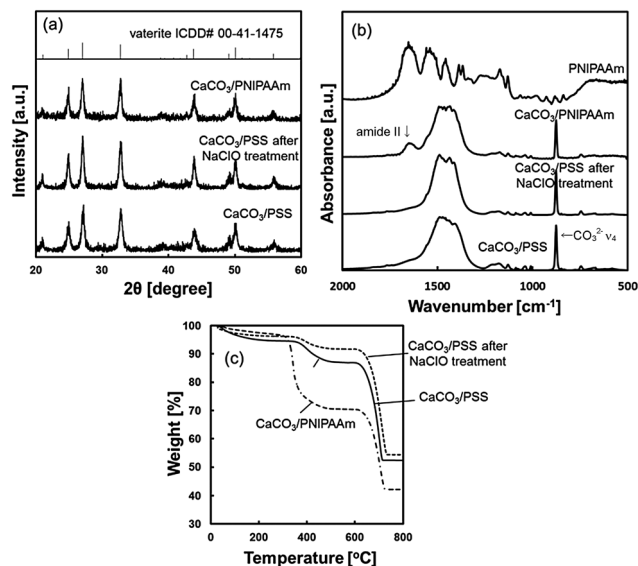


Fig. 2 XRD patterns (a), FT-IR spectra (b), and TG curves (c) of the CaCO₃-polymer composite microspheres.

PNIPAAm in the CaCO₃ microspheres after the introduction of the monomer with a cross-linker and subsequent UV irradiation in hexane containing the initiator. The removal of PSS from the CaCO₃ microspheres and the introduction of PNIPAAm into the interparticle space were supported by variation in the TG curves (Fig. 2c). The mass reduction in the range from 350 to 450 °C was ascribed to combustion of the polymers contained in the microspheres. The original microspheres had *ca.* 10 wt% of PSS, and half of them were lost by the NaClO treatment. The polymerization induced more than 20 wt% of PNIPAAm in the spheres. This means that the surface of the spheres was almost completely covered with the polymer, as shown in Fig. 1. The polymorph of CaCO₃ was maintained after the removal of PSS and the introduction of PNIPAAm.

The microspheres were dispersed in water and slowly precipitated for several hours at 25 °C (Fig. 3a and c). On the other hand, they were immediately precipitated in a few minutes through aggregation at 60 °C (Fig. 3b and d). The monolayer assembly of the microspheres was achieved on the hydrophobic surface of an alkyl-modified glass substrate by dropping of the dispersion and subsequent drying (Fig. 4a). We observed a partial hexagonal arrangement of the microspheres connected with each other *via* the sticky polymer in the monolayer (Fig. 4c). The ordered structure of the microspheres was firmly fixed on the hydrophobic surface in water at 60 °C. On the other hand, the spheres were rapidly removed from the surface with ultrasonic agitation in water at 25 °C (Fig. 4b). The hydrophobic polymer chains of the shell are entangled with each other at the interface of the spheres and the alkyl chains of the hydrophobic surface.

We prepared a toluene–water–nitrobenzene system to clarify the property of the microspheres (Fig. 5). The water phase was turbid due to the dispersion of the microspheres at 20 °C. On the other hand, the aqueous part became clear and the toluene

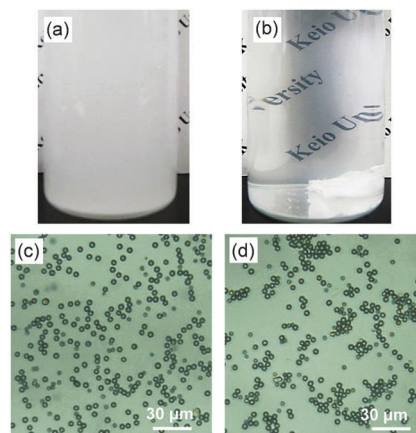


Fig. 3 Macroscopic and microscopic images of the dispersion of CaCO₃-PNIPAAm composites in water at 25 °C (a, c) and 60 °C (b, d).

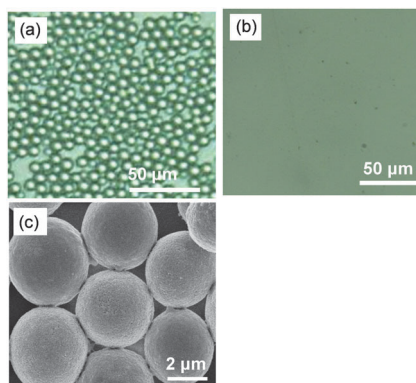


Fig. 4 Optical micrographs (a, b) and SEM image (c) of the CaCO₃-PNIPAAm composites on an alkyl-modified glass substrate after washing in water by sonication at 60 °C (a, c) and 25 °C (b).

and nitrobenzene phases clouded at 90 °C. (The high temperature was used to induce the change of the system immediately.) This means that the microspheres that had moved into the organic phases were stably dispersed in the media above LCST. This behaviour was completely reversible by a swing in temperature. Because the PNIPAAm shell covering the porous carbonate body is hydrophilic and swells with water below LCST, the microspheres are dominantly dispersed in water. The hydrophobic shell above LCST induces aggregation in water and leads to a stable dispersion in organic media of the microspheres. Thus, the microspheres were shuttlecocked between water and hydrophobic media with switchable hydrophobicity of the shell layer by a swing in temperature. However it took several hours to achieve the transfer of the microspheres between two phases with ultrasonic agitation, although the microspheres were immediately precipitated in the original phase within a few minutes by increasing or decreasing the temperature. The gentle motion of the microspheres is ascribed to a low permeability of the dispersant.

We prepared a toluene–water system containing a hydrophobic pigment, copper phthalocyanine (CuPh) (Fig. 6). The microspheres were dispersed in water below LCST and moved into the organic phases above LCST (90 °C). The microspheres



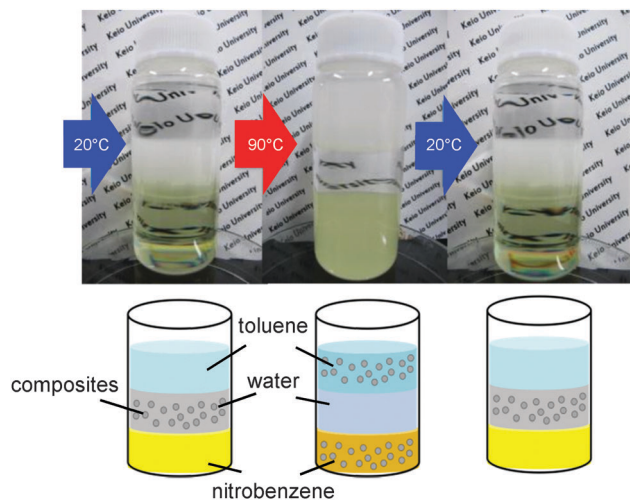


Fig. 5 Photographs and schematic illustration of a toluene–water–nitrobenzene system containing the CaCO_3 –PNIPAAm composites with a swing in temperature.

moved back from the organic phase to water upon decreasing the temperature to 20 °C. We observed that the water phase became pale blue with the dispersion of the microspheres, indicating that the pigment was captured by the CaCO_3 –PNIPAAm microspheres in the toluene solution at 90 °C. The microspheres that captured the pigment were dispersive in water below LCST. The saturated CuPh content in the composite microspheres was estimated to be about $1.2 \times 10^{-4} \text{ mol g}^{-1}$. After the pigment-capturing microspheres were removed from the water, we redispersed them into a pure toluene–water system

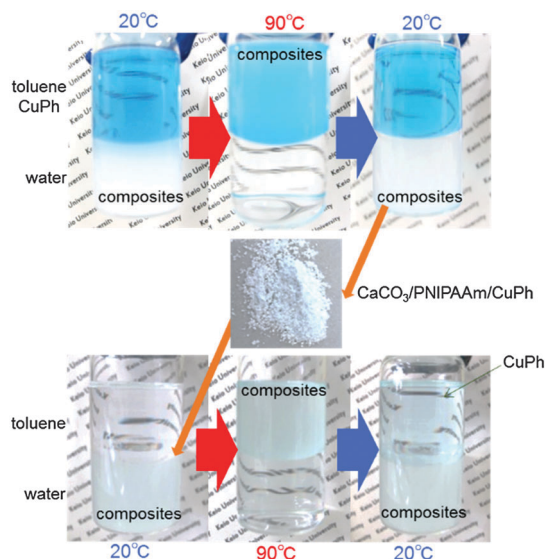


Fig. 6 Photographs of a toluene–water system containing the CaCO_3 –PNIPAAm composites and CuPh with a swing in temperature. CuPh was trapped by the CaCO_3 –PNIPAAm composites in a toluene phase transport at 90 °C and transported to water at 20 °C. The concentration of CuPh trapped in the dried composites was estimated to be $1.2 \times 10^{-4} \text{ mol g}^{-1}$. About 70% of CuPh in the CaCO_3 –PNIPAAm composites was released to another toluene phase with a swing in temperature.

below LCST. When the temperature was increased, the microspheres were transported into the fresh toluene phase. After removal of the microspheres by decreasing the temperature, the toluene phase became blue due to the release of the pigment in the organic phase from the microsphere. The microspheres delivered and released the hydrophobic molecules to a pure organic medium above LCST. About 70% of the CuPh captured in the microspheres was released in the organic phase.

We prepared a toluene–water–toluene system containing CuPh in the left toluene phase using a U-tube (Fig. 7). The microspheres dispersed in water below LCST moved into the organic phases above LCST (90 °C). The microspheres moved back from the organic phase to water when the temperature was decreased to 20 °C. The CuPh concentration in the right toluene phase increased and became the same as that in the left toluene phase through 11 cycles of the shuttlecock behaviour. Therefore, the thermosensitive microspheres play a role as an active carrier delivering specific hydrophobic agents between two organic phases separated by water.

The functionality of the composite microspheres was confirmed using bare CaCO_3 microspheres without PNIPAAm and pure PNIPAAm without CaCO_3 . We prepared the bare CaCO_3 microspheres and pure PNIPAAm from the composite microspheres by the dissolution of PNIPAAm with NaClO and CaCO_3 with diluted hydrochloric acid, respectively. The blue pigment stayed in the left toluene phase after the temperature swing in the toluene–water–toluene system. This means that the composite structure consisting of the mesostructured framework of CaCO_3 and the polymer shell is essential for the thermosensitive trapping performance of hydrophobic molecules. The hydrophobic nature of the polymer shell attracts hydrophobic molecules in organic media above LCST. The hydrophobic molecules are trapped in the nanopores of the inorganic framework with the hydrophilic polymer shell below LCST. Thus, the composite microspheres containing hydrophobic molecules are dispersed in water.

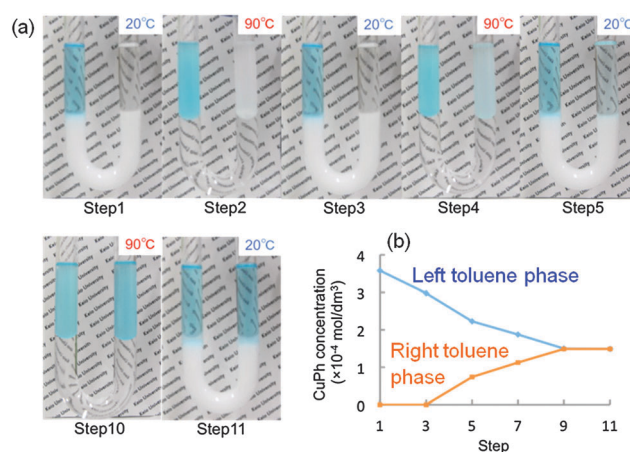


Fig. 7 Photographs of a toluene–water–toluene system containing the CaCO_3 –PNIPAAm composites and CuPh in a U-tube (a). CuPh was transported with the CaCO_3 –PNIPAAm composites from the left toluene phase into the right toluene phase through the water phase by a swing in temperature. The CuPh concentration of the left and right toluene phases changed with the cycle of temperature (b).



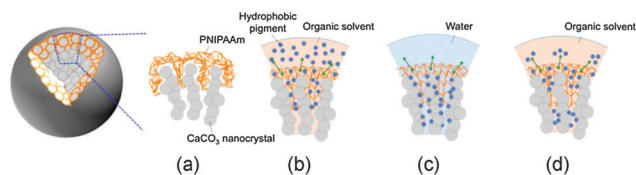


Fig. 8 Schematic illustration of a trap-release mechanism of the hydrophobic pigment on the CaCO_3 -PNIPAAm composites (a). The hydrophobic pigment is trapped by PNIPAAm with swelling by the organic medium above LCST (b). The pigment is kept in the nanopores in water below LCST (c). The pigment is released into the organic phase with swelling by the organic medium above LCST (d).

The hydrophobic molecules are released through the hydrophobic polymer shell to another organic medium above LCST. A series of trap-release mechanisms is illustrated in Fig. 8. Microspheres are stably dispersed in water because PNIPAAm swells below LCST. The hydrophobic pigment is captured by the polymer shell covering the CaCO_3 framework above LCST. In water, the trapped hydrophobic pigment is protected in the nanopores of the framework below LCST. The pigment is released into the organic media with the swelling of the polymer above LCST. However, the pigments trapped in the deep region of the nanopores were not released in the organic media.

The dispersivity and the fixing ability of the microspheres are controllable with the swing in temperature. This suggests that specific organic agents can be delivered to hydrophobic media at a high temperature using the thermosensitive microspheres. Because the size of the CaCO_3 spheres¹⁹ and the property of the thermosensitive polymer can be designed, the composite microspheres could be developed into a novel drug delivery system as an active carrier.

Conclusions

Monodispersed thermosensitive microcomposites consisting of a rigid inorganic porous core and a soft functional shell were synthesized by the combination of vaterite CaCO_3 microspheres and poly(*N*-isopropylacrylamide). Their dispersivity in water, their fixing ability on a hydrophobic surface, and their molecular-trapping performance were switchable by temperature. The functional composites would be applicable to a novel drug delivery or transport system.

Acknowledgements

This work was partially supported by a Grant-in-Aid for Scientific Research (no. 22107010) on Innovative Areas of "Fusion Materials: Creative Development of Materials and Exploration of their Function through Molecular Control" (area no. 2206) from the Ministry of Education, Culture, Sports, Science and Technology from Japan Society of the Promotion of Science.

Notes and references

- 1 S. Mann, *Nature*, 1988, **332**, 119.
- 2 L. Addadi and S. Weiner, *Angew. Chem., Int. Ed. Engl.*, 1992, **31**, 153.
- 3 S. Mann, *Nature*, 1993, **365**, 499.
- 4 J. Aizenberg, J. C. Weaver, M. S. Thanawala, V. C. Sundar, D. E. Morse and P. Fratzl, *Science*, 2005, **309**, 275.
- 5 S. I. Stupp and P. V. Braun, *Science*, 2007, **277**, 1242.
- 6 S. Weiner and L. Addadi, *Annu. Rev. Mater. Sci.*, 2011, **41**, 21.
- 7 A. W. Xu, M. Antonietti, S. H. Yu and H. Cölfen, *Adv. Mater.*, 2008, **20**, 1333.
- 8 Y. Politi, T. Arad, E. Klein, S. Weiner and L. Addadi, *Science*, 2004, **306**, 1161.
- 9 E. Beniash, J. Aizenberg, L. Addadi and S. Weiner, *Proc. R. Soc. London, Ser. B*, 1997, **264**, 461.
- 10 Y. Oaki, A. Kotachi, T. Miura and H. Imai, *Adv. Funct. Mater.*, 2006, **16**, 1633.
- 11 Y. Oaki and H. Imai, *Angew. Chem., Int. Ed.*, 2005, **44**, 6571.
- 12 Y. Oaki and H. Imai, *Small*, 2006, **2**, 66.
- 13 T. Kokubu, Y. Oaki, E. Hosono, H. Zhou and H. Imai, *Adv. Funct. Mater.*, 2011, **21**, 3673.
- 14 K. Naka, S. C. Huang and Y. Chujo, *Langmuir*, 2006, **22**, 7760.
- 15 X. H. Guo, S. H. Yu and G. B. Cai, *Angew. Chem., Int. Ed.*, 2006, **45**, 3977.
- 16 H. Cölfen and M. Antonietti, *Angew. Chem., Int. Ed.*, 2005, **44**, 5576.
- 17 M. G. Page and H. Cölfen, *Cryst. Growth Des.*, 2006, **6**, 1915.
- 18 M. S. Mo, S. H. Lim, Y. W. Mai, R. K. Zheng and S. P. Ringer, *Adv. Mater.*, 2008, **20**, 339.
- 19 H. Imai, N. Tochimoto, Y. Nishino, Y. Takezawa and Y. Oaki, *Cryst. Growth Des.*, 2012, **12**, 876.
- 20 Y. Oaki and H. Imai, *Adv. Funct. Mater.*, 2005, **15**, 1407.
- 21 Y. Oaki and H. Imai, *Chem. Commun.*, 2005, 6011.
- 22 L. Meijer, A. L. Skaltsounis, P. Magiatis, P. Polychronopoulos, M. Knockaert, M. Leost, X. P. Ryan, C. A. Vonica, A. Brivanlou, R. Dajani, C. Crovace, C. Tarricone, A. Musacchio, S. M. Roe, L. Pearl and P. Greengard, *Chem. Biol.*, 2003, **10**, 1255.
- 23 A. Varshney, B. Ahmad, G. Rabbani, V. Kumar, S. Yadav and R. H. Khan, *Amino Acids*, 2010, **39**, 899.
- 24 H. G. Schild, *Prog. Polym. Sci.*, 1992, **17**, 163.
- 25 R. Liu, M. Fraylich and B. R. Saunders, *Colloid Polym. Sci.*, 2009, **287**, 627.
- 26 S. Tsuji and H. Kawaguchi, *Langmuir*, 2004, **20**, 2449.
- 27 S. Tsuji and H. Kawaguchi, *Langmuir*, 2005, **21**, 8439.
- 28 M. Nakayama, T. Okano, T. Miyazaki, F. Kohori, K. Sakai and M. Yokoyama, *J. Controlled Release*, 2006, **115**, 46.
- 29 J. Qin, Y. S. Jo, J. E. Ihm, D. K. Kim and M. Muhammed, *Langmuir*, 2005, **21**, 9346.
- 30 Y. Z. You, K. K. Kalebaila, S. L. Brock and D. Oupicky, *Chem. Mater.*, 2008, **20**, 3354.
- 31 K. Ukigaya, Y. Oaki and H. Imai, *Chem. Lett.*, 2012, **41**, 507.
- 32 C. D. Jones and L. A. Lyon, *J. Am. Chem. Soc.*, 2003, **125**, 460.

