



Cite this: *Chem. Soc. Rev.*, 2025, 54, 3578

Synthesis innovations for crystallizing covalent organic framework thin films on biological and non-biological substrates

Ashok Kumar Mahato,^{ab} Satyadip Paul^{ab} and Rahul Banerjee  ^{ab}

Thin film technology has emerged as a pivotal field with numerous industrial applications. Depending on their properties—such as magnetic characteristics, conductivity, architectural structure, stability, and functional backbones—thin films are widely utilized in optoelectronics, thin-film coatings, solar cells, energy storage devices, semiconductors, and separation applications. However, for all these applications, thin films must be securely attached to specific substrates, and substrate compatibility with both the thin film and the film-growth process is crucial for optimal performance. In this review, we emphasize the significance of growing thin films, particularly covalent organic framework (COF) thin films, on suitable substrates tailored for various applications. For separation technologies, polymer thin films are commonly fabricated on porous polymeric or metal-based membranes. In contrast, thin films of metals and metal oxides are typically deposited on conducting substrates, serving as current collectors for energy storage devices. Semiconductor thin films, on the other hand, are often grown on silicon or glass substrates for transistor applications. Emerging COF thin films, with their tunable properties, well-defined pore channels, and versatile functional backbones, have demonstrated exceptional potential in separation, energy storage, and electronic and optoelectronic applications. However, the interplay between COF thin films and the substrates, as well as the compatibility of growth conditions, remains underexplored. Studies investigating COF thin film growth on substrates such as metals, metal oxides, glass, silicon, polymers, ITO, and FTO have provided insights into substrate properties that promote superior film growth. The quality of the film formed on these substrates significantly influences performance in applications. Additionally, we discuss the stabilization of biological substrates, like peptide-based biomimetic catalysts and enzymes, which often suffer from instability in non-aqueous environments, limiting their industrial use. Growing COF membranes on these biological substrates can enhance their stability under harsh conditions. We also highlight techniques for growing COF membranes on biological substrates, ensuring the preservation of their structural integrity and functional properties.

Received 5th December 2024

DOI: 10.1039/d4cs01222d

rsc.li/chem-soc-rev

^a Department of Chemical Sciences, Indian Institute of Science Education and Research, Kolkata, Mohanpur 741246, India. E-mail: r.banerjee@iiserkol.ac.in

^b Centre for Advanced Functional Materials, Indian Institute of Science Education and Research, Kolkata, Mohanpur 741246, India



Ashok Kumar Mahato

Ashok Kumar Mahato received his MSc degree in chemistry from the Indian Association for the Cultivation of Science (IACS), Kolkata, in 2019. He obtained his PhD in chemical science in 2024 under the supervision of Prof. Rahul Banerjee at the Indian Institute of Science Education and Research (IISER) Kolkata, India. His research interests cover the design, synthesis and applications of covalent organic framework thin films.



Satyadip Paul

Satyadip Paul received his MSc degree in chemistry from the Indian Institute of Technology (IIT), Madras in 2017. He obtained his PhD in chemical science in 2024 under the supervision of Prof. Rahul Banerjee at the Indian Institute of Science Education and Research (IISER) Kolkata, India. His research focuses on enzyme immobilization, heterogeneous biocatalysis, bioconjugation, and protein chemistry.



1. Introduction

Thin films known for their exceptional functional diversity, including polymers, metals, metal oxides, organic and metal-organic materials, are extensively used in electronics, optoelectronics, electrochemical devices, and separation applications.^{1–9} Covalent organic framework (COF) thin films represent an exciting advancement in thin film technology, exhibiting remarkable versatility and high-performance potential across diverse industrial sectors.^{10–16} These films are characterized by their high crystallinity, tunable pore sizes, and customizable functional groups, which distinguish them from conventional thin films.^{17–19} The unique structures of COF thin films set them apart from traditional thin films made from polymers, organic molecules, metals, and metal oxides (Fig. 1(a) and (b)). Their distinct crystalline architecture and modular design enable precise control over pore channels, redox-active sites, conductive pathways, and catalytic centres, making them well-suited for targeted applications such as selective ion transport, molecular sieving, electronic devices, and energy storage systems.^{20,21}

In any thin film-related applications, integration of the film with a suitable substrate is crucial.^{22,23} Substrates provide essential structural support, preserve film integrity, enhance electron and mass transport, and stabilize performance under various operating conditions. The interaction between the film and substrate influences the crystallization and self-assembly of crystallites during film growth, affecting critical performance metrics, such as mechanical strength and operational durability.^{24–27} This is particularly vital for direct film growth, as it reduces macroscopic defects and improves adhesion, enhancing film functionality and operational durability. Various synthetic techniques, including drop casting, spin coating, vapor deposition, solvothermal, atomic layer deposition and electrochemical deposition, have been employed to grow COF films on substrates (Fig. 1(c)).^{28,29} Substrates are chosen based on their properties such as porosity, conductivity, magnetic

properties, wettability and surface functionalities as well as their stability under growth conditions. Common substrates include polymers, metals, metal oxides, carbon-based materials, silicon wafers, and glass. Furthermore, techniques like interfacial crystallization enable COF thin film growth at liquid–liquid or liquid–air interfaces. However, transferring such thin films to substrates often leads to cracks and defects, limiting their practical usability. As a result, the direct growth of COF films on appropriate substrates has become a preferred approach over traditional film transfer methods, which often introduce micro-cracks, result in poor adherence, and reduce overall film quality. Therefore, it is crucial to ensure the substrate compatibility of a thin film and also an optimal film growth process tailored to the desired substrate.

This review explores recent advancements in COF thin film growth directly on various substrates, focusing on how substrate–film interactions, synthesis techniques, and substrate selection contribute to producing high-quality, durable films. It also discusses the use of COF thin films on biological substrates.^{30–35} By cladding COF films on biocatalysts such as enzymes, we can overcome the stability challenges these biological materials face in non-aqueous environments. This innovation expands the operational stability of biocatalysts, opening up new possibilities for stable, functional biocatalytic systems in industrial settings. We aim to demonstrate how COF thin films can potentially transform industrial applications, offering customized solutions that address the functional requirements of next-generation technologies.

2. Thin films grown on substrates

This review focuses on the synthesis and applications of COF thin films grown on or adhered to various substrates. Highlighting the importance of substrate compatibility and growth processes, we focus on the applications of COF thin films on various substrates, and the advantages and disadvantages of different synthesis methods. Although numerous methods exist for synthesizing COF thin films on substrates challenges persist, including suboptimal film quality, limited material diversity, and complex experimental setups. This review aims to provide insights into synthesis techniques for COF thin films on substrates to achieve optimal performance.

2.1 Primary applications of various thin films on substrates

Polymer thin films are grown on different substrates to serve a variety of applications, including membrane separation, electronic and optoelectronic devices, packaging, electrochemical devices and protective coatings.^{36–40} Polyamide thin films, for instance, are often fabricated on microporous substrates such as polyethersulfone and polytetrafluoroethylene (PTFE) for separation applications (Fig. 2(a)).^{23,41,42} Organic thin-film transistors (OTFTs) frequently utilize polythiophene-based polymers, where thin polythiophene layers are deposited on silicon wafers and glass substrates to create the active semiconductor layer for transistor applications.^{43–45} This approach




Rahul Banerjee

purification, energy storage and conversion, and separation applications.


Prof. Rahul Banerjee has been a professor at IISER Kolkata since 2017. His research interests include crystallography, reticular chemistry and organic material synthesis. His group has developed unique methodologies of synthesizing covalent organic frameworks with various morphologies and exceptional chemical stability. His group further utilized the covalent organic frameworks (COFs) for carbon sequestration, water



(a) Growth of COF thin films on substrates:

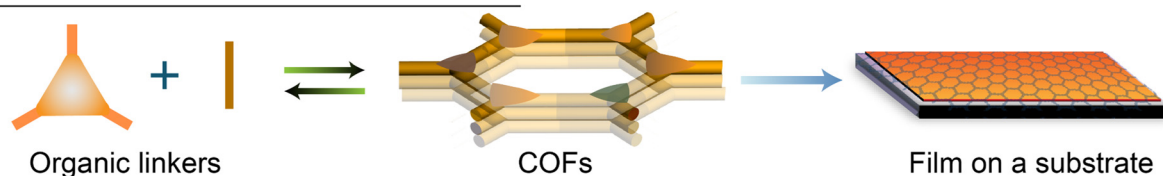

(b) Different types of thin films:

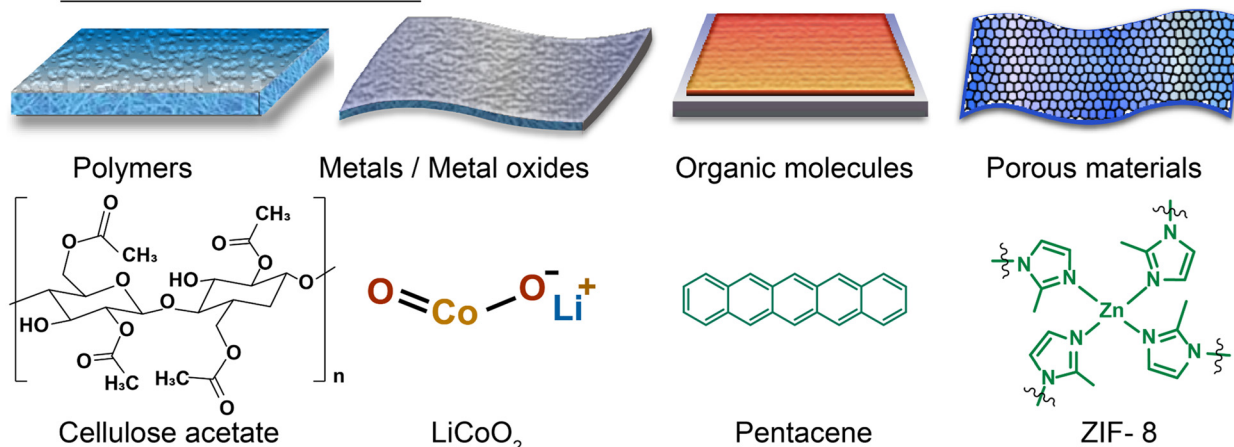

(c) Commonly used techniques for thin films synthesis on substrates:

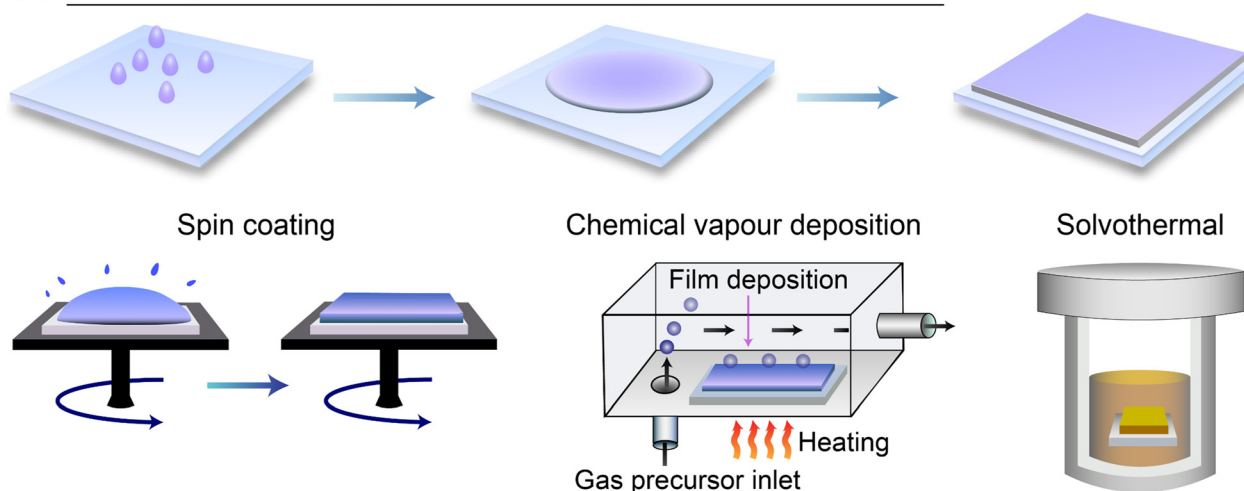


Fig. 1 (a) Schematic representation of synthesis of covalent organic frameworks (COFs) and their thin-films on substrates. (b) Commonly used materials for thin film fabrication. (c) General techniques of thin film synthesis.

highlights the adaptability of polymer thin films across a spectrum of substrates, enabling advancements in electronics, environmental protection, and energy storage solutions.

Metals and metal oxides are deposited as thin films to form the active functional layers in energy storage systems, electronic devices, optoelectronic devices, and fuel cells as catalyst layers.^{46–58} Commonly used materials for these applications include lithium, zinc, nickel, platinum, lithium cobalt oxides (LiCoO_2), lithium manganese oxides (LiMn_2O_4), LiFePO_4 , and LiNiPO_4 , and zinc oxide (ZnO) typically deposited as thin films onto diverse substrates.^{59–68} Since the commercialization of Li


batteries, lithium cobalt oxide, with a theoretical capacity of 274 mA h g^{-1} , has long been a popular cathode material in energy storage devices, particularly lithium-ion batteries (Fig. 2(b)).^{69,70} Methods like vapor deposition, atomic layer deposition, and electrodeposition are often employed for these coatings, primarily on copper and aluminium foils. The vapor deposition technique is versatile for growing uniform thin films with good adhesion with substrates. However, this method is often limited to types of substrates. Atomic layer deposition and electrodeposition can be performed at lower temperatures with good control over film thickness. These



Primary applications of various thin films on substrates:


(a) Polymer:

Membrane separation and energy applications

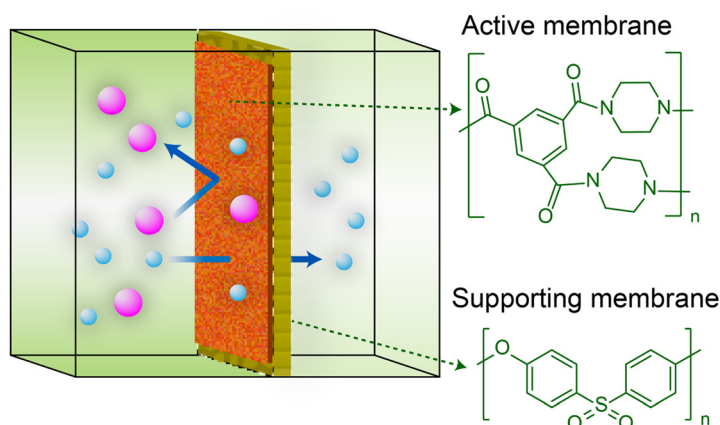


(b) Metal and metal oxides :

Energy applications

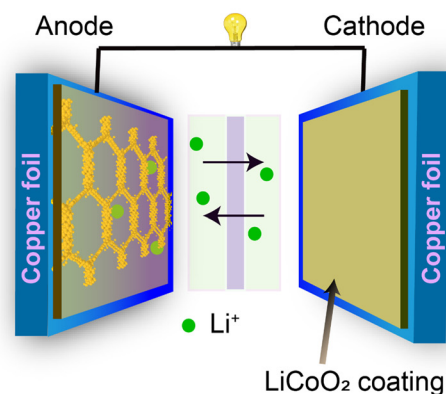

(c) Organic molecules:

Organic electronics

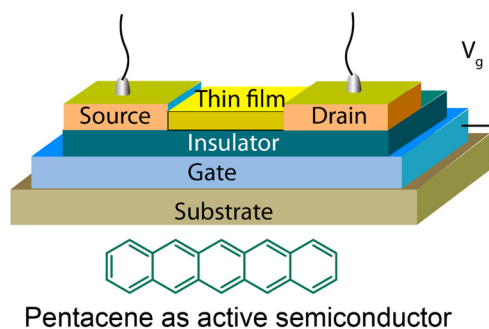

(d) Covalent organic frameworks (COFs):

Membrane separation and energy applications

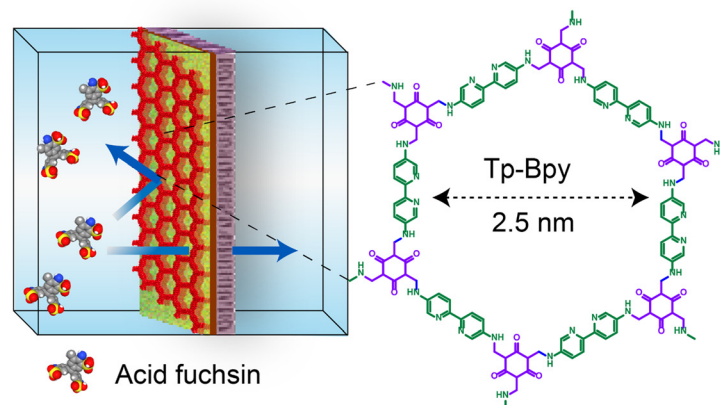


Fig. 2 The applications of various thin films. Applications of (a) polymer thin films in membrane separation, (b) metal and metal oxide films in energy storage applications, (c) organic molecules in transistor applications and (d) COFs in membrane separation.

methods are also limited to materials compatibility. The selection of deposition techniques mostly depends on the stability and properties of the materials and the substrates.

Organic molecules are extensively applied in thin film synthesis for applications in electronic and energy storage devices. Organic molecules are widely utilized in organic field effect transistors because of efficient charge carrier mobility and desired semiconducting properties.^{71,72} Pentacene, a well-known organic molecule, is widely used to fabricate OFETs (Fig. 2(c)).⁷³ These small molecules are typically deposited as thin films on substrates like SiO₂ and glass through spin coating, which provides a uniform layer essential for electronic and optoelectronic applications. Redox-active organic molecules are also deposited as thin films to fabricate the electrodes in batteries.^{74–76}

2.2 COF thin films on substrates


Current research efforts are increasingly focused on the sustainable development of metal-free active materials for various applications. Researchers have made significant advances in creating metal-free systems, such as organocatalysts and organophotocatalysts, as well as small and complex molecules for energy storage and optoelectronics. Among these materials, crystalline polymers stand out due to their unique properties conferred by crystallinity, often resulting in novel functions.^{77–79} COFs comprise symmetric organic linkers covalently connected to form extended two-dimensional (2D) or three-dimensional (3D) structures, adopting various geometries including hexagonal, tetragonal, rhombic, kagome, and triangular arrangements.^{80–85} The physicochemical properties, catalytic activities, and morphologies of COFs are further tuned




by selecting appropriate linkers, synthesis methods, and post-synthesis modifications. Interestingly, many such applications, including separation and energy storage, specifically require porous crystalline films (Fig. 2(d)). The insolubility and limited processability of bulk COF powders present significant obstacles to membrane fabrication, restricting their practical use.¹⁵ For instance, anthraquinone-based COF powder blended with carbon black demonstrated improved electrode performance; however, calculations revealed that only 2.5% of the anthraquinone moieties were electrochemically accessible due to the random orientation of the COF powder.⁸⁶ Consequently, crystalline and oriented COF thin films have emerged as highly promising materials, offering tunable properties suitable for practical applications.

The synthesis technique is crucial for producing high-quality COF thin films, as it directly impacts their properties and performance.^{87–92} The growth and assembly of COF crystallites depend heavily on the chosen method (Fig. 3(a)). Unlike polymer thin films, which often exhibit random orientations, COF thin films have well-defined pore channels with adjustable pore diameters (Fig. 3(b)). This tunability enables molecular sieving, allowing for the selective separation of molecules based on size.^{93–99} Furthermore, COF thin films can exhibit different pore structures, depending on their geometric configuration—whether tetragonal, hexagonal, kagome, rhombic, or trigonal—which can be tailored for specific separation and other applications (Fig. 3(c) and (d)). Typically, COF thin films


(a) Fabrication of COF thin films:

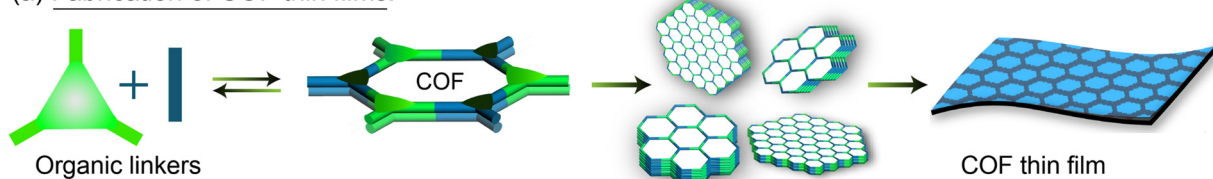

(b) Benefits of COF thin films over polymer films:

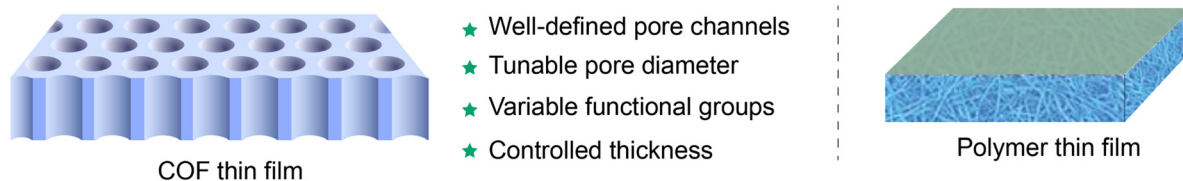

(c) COF thin films with various pore diameter:

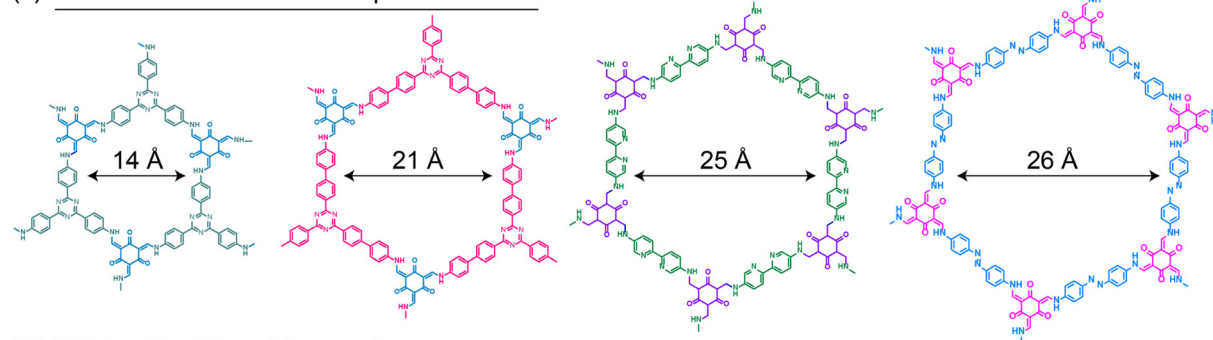

(d) COFs with different types of pores:

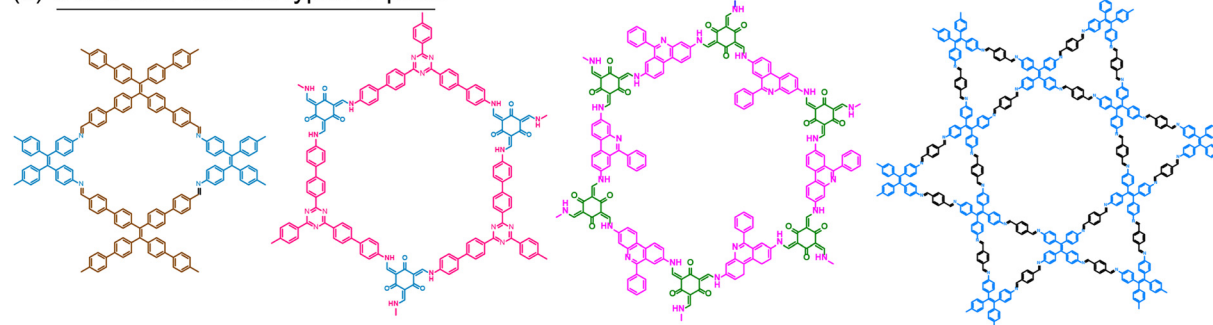


Fig. 3 Schematic representation of (a) thin film fabrication using organic linkers and (b) advantages of COF thin films over polymer thin films. (c) Chem-draw structures of COFs with different pore diameters. (d) Chem-draw structures of COFs with various types of pores.



possess semiconducting properties, with band gaps ranging from 0.5 eV to 2.8 eV. The band gap can be easily adjusted to meet the requirements of various applications by modifying the functional backbone structures.^{100–103} This level of control over structural and electronic properties positions COF thin films as versatile and valuable materials for a wide array of technological advancements.

2.2.1 Selection of substrates. Quality of film growth is mostly affected by the growth conditions and properties of the substrates. In addition, the optimal film growth eventually improves the performances in thin film applications.

To examine the growth of COF films on substrates, we utilized residual crystallization processes to synthesize COF thin films (TpAzo and TpDPP) on several substrates with different wettabilities (ITO, FTO, borosilicate glass, silicon wafer, metallic copper and polytetrafluoroethylene).²⁶ Under the same reaction conditions for all substrates, we observed a superior film growth of TpAzo and TpDPP COFs on a glass substrate. Crystallinity and porosity of the thin films grown on hydrophilic substrates are much better than the thin films grown on hydrophobic substrates. We anticipate that the hydrophilic amine and aldehyde functional groups on the crystallite surface favour the assembly and crystallization on hydrophilic surfaces (like glass) during the reaction. Therefore, it is crucial to realize the nature of substrates and COF crystallites to obtain the optimal film growth on substrates. Moreover, it is well known that the crystallinity and porosity are the important parameters for the performances in membrane-based applications. A β -ketoenamine-based crystalline COF (TFP-DHF) thin film was fabricated on a porous anodic aluminum oxide substrate, which exhibited improved organic solvent permeability by 100 times compared to the amorphous membrane synthesized by the same process.¹⁰⁴ This suggests that the crystallinity plays an important role in separation applications. Therefore, the substrate selection is crucial as it greatly influences the crystallinity, porosity, and, eventually, the performance of the thin films. Furthermore, the substrates are often modified by introducing several functionalized molecules to react with the precursor molecules and then drive the crystallization for a better-quality film growth. For example, aldehyde-modified and dual-amino-modified Al_2O_3 supports have been used to grow ACOF-1 and COF-LZU1-ACOF-1 composite membranes for improved gas separation efficiency.^{105,106}

Stability of substrates is another important parameter to be considered under the film growth conditions. Fragile substrates especially biological substrates are not stable under harsh reaction conditions like solvothermal and other methods involving high temperature and organic solvents. For such fragile substrates, it is highly desirable to design the reaction system associated with aqueous media. For example, we developed a cladding technique to grow a COF layer on peptide-based biomimetic catalysts.²⁷ During the reaction we take the biomimetic catalysts in the water layer to preserve their structure and activity.

2.2.2 Fabrication of COF thin films on different substrates. Direct growth ensures stronger adhesion between the COF thin

film and the substrate, which enhances charge carrier mobility at the film–substrate interface in electronic devices and improves efficiency in separation applications. Understanding the mechanisms of film growth and the interactions between COF crystallites and substrates is crucial for optimizing substrate compatibility and achieving high-quality film deposition (Fig. 4(a)). COF thin films have been successfully grown on a range of substrates, including graphene-based surfaces, glass, metals, metal oxides, and polymers, using various synthesis techniques. The solvothermal method was first employed to synthesize COF thin films on single-layer graphene (SLG) attached to supporting substrates, such as SLG/Cu, SLG/SiC, and SLG/SiO₂ (Fig. 4(b)).^{107,108} This approach enabled the synthesis of COF-5, TP, and NiPc-PBBA COF thin films on the substrates with vertical alignment. Different film thicknesses of COF-5 on the substrates, 195 ± 20 nm (30 min film growth on SLG/Cu), 94 ± 5 nm (2 h film growth on SLG/SiO₂) and 73 ± 3 nm (8 h film growth on SLG/SiC), suggest that the COF nucleation and film growth are highly susceptible to the nature of substrates.


While the solvothermal method facilitates easy film synthesis on various supports, it often leads to issues like bulk powder contamination and inhomogeneous film growth. To address these challenges, various techniques have been employed for COF thin film synthesis. The vapor-assisted conversion process, used to grow BDT-COF, COF-5, and pyrene-COF thin films at room temperature (Fig. 4(c)), involves drop-casting dissolved precursor solutions onto a glass substrate and placing it in a desiccator with an open solvent vial containing mesitylene and dioxane. This method produces thick films ranging from 300 nm to 7.5 μm after 72 hours of crystallization, which is beneficial for substrates unable to endure the harsh conditions of solvothermal synthesis.¹⁰⁹ However, achieving thin films using this approach remains challenging and restricts specific applications. Electrophoretic deposition is another technique for fabricating COF films and coatings on conducting surfaces (Fig. 4(d)). Using this method, COF-5, COF-300, and BDT-ETTA COFs with different functional groups (imine and boronate ester bonds) are synthesized on metal and metal oxide substrates. Electrodes are immersed in nanoparticle suspensions of bulk COFs, with an applied bias ranging from 100 to 900 V cm^{-1} . This technique enables rapid, large-area film growth (up to 25 cm^2) within just 2 minutes, with thicknesses varying from 400 nm to 24 μm . The film thickness can be precisely controlled by adjusting parameters such as electrode potential, deposition time, and particle concentration.¹¹⁰

Despite the advantages of quick and extensive film growth, the requirement for high voltage is a limitation.


Another well-known COF thin film fabrication method is the direct solvent evaporation of a COF solution or slurry (Fig. 4(e)). Preparing a highly processable COF particle solution is essential to ensure film quality. This method involves creating stable colloidal suspensions of COF-5 using co-solvents, achieving a stable suspension that remains homogeneous for weeks without precipitation, even when cooled. Solvent evaporation of the




(a) Growth of COF thin film on supports:

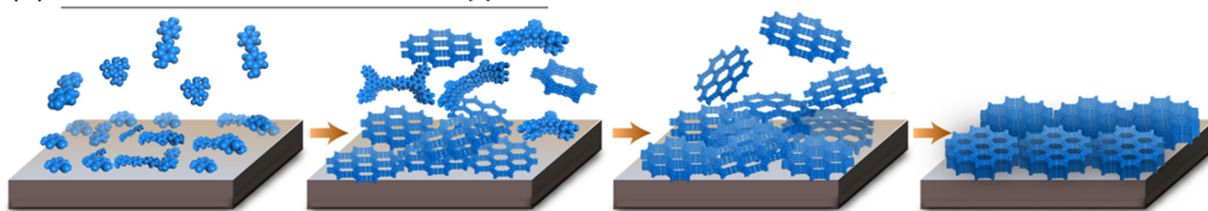


(b) Solvothermal synthesis:

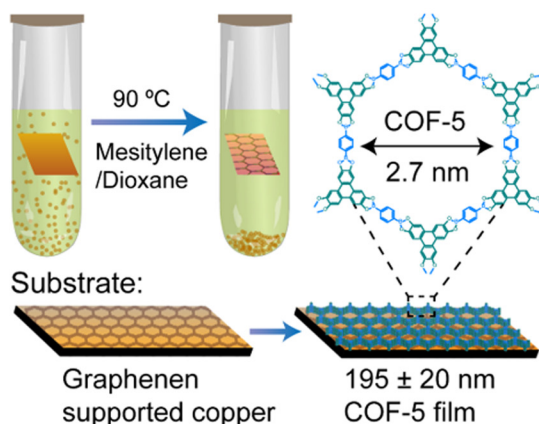

(c) Vapor-assisted conversion:

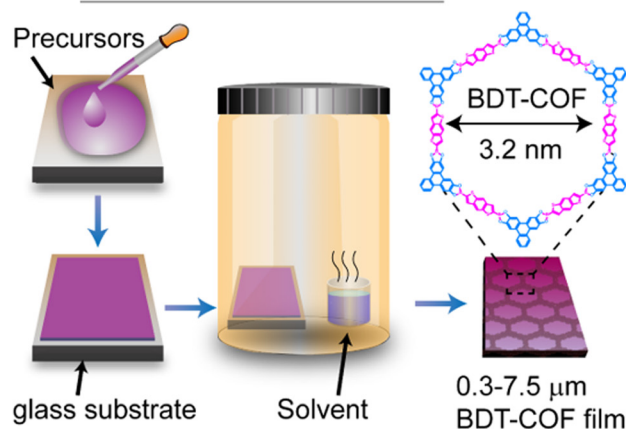

(d) Electrophoretic deposition:

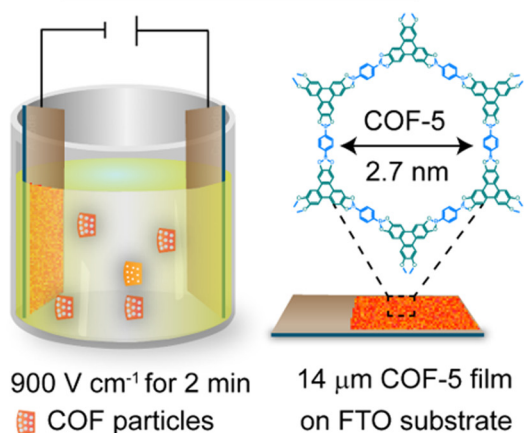

(e) Solvent evaporation:

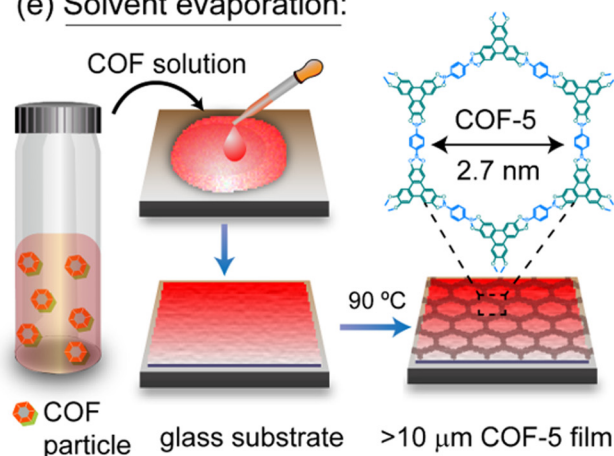


Fig. 4 Schematic representation of (a) the growth mechanism on supports, (b) solvothermal synthesis of COF thin films on single layer graphene, (c) vapour assisted synthesis on a glass substrate, (d) electrophoretic deposition on conducting supports, (e) solvent evaporation technique for film synthesis on a glass support. Fig. 4(a) is adapted from ref. 24 with permission from the Royal Society of Chemistry, Copyright 2017.

COF-5 colloidal solution at 90 °C results in film growth on glass substrates, producing films with thicknesses exceeding 10 μm.¹¹¹ However, this method requires the substrate to be compatible with the conditions of colloidal synthesis, underscoring the importance of substrate selection.

A modified solvothermal approach was utilized to synthesize crystalline, oriented thin films on an Au-working electrode, while the conventional solvothermal process provided only nondiffracting thin films (Fig. 5(a)).¹¹² This method provides excellent improvement in capacitance when thin films are used

as electrode materials compared to the randomly oriented powdered COFs. Slow addition of a trialdehyde precursor solution (TFP in DMF) into the diamine (DAAQ) solution of DMF at 90 °C was performed to avoid the rapid crystallization and produce a crystalline, oriented DAAQ–TFP thin film on an Au-substrate. Such oriented thin film growth on the Au electrode helped in accessing the large percentage of redox-active functional groups electrochemically, providing an areal capacitance of 3.0 mF cm⁻². In contrast, the COF powder-modified electrodes showed only 0.4 mF cm⁻². Such research findings of



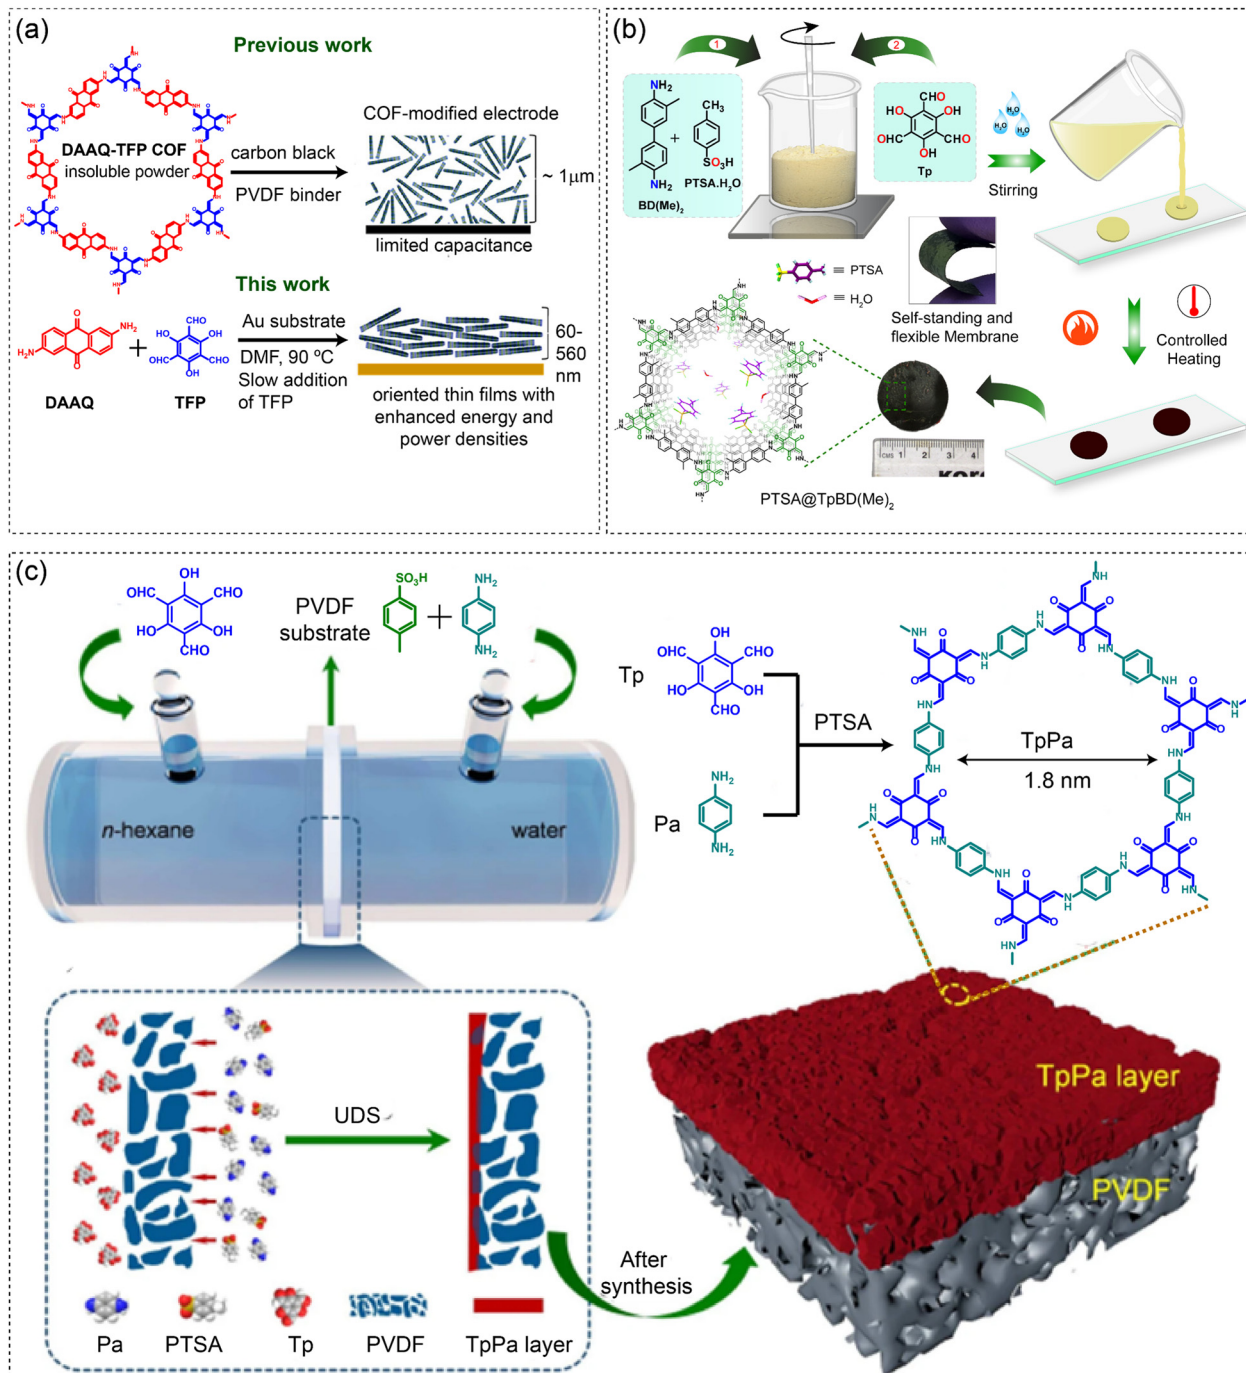


Fig. 5 Synthesis of COF films on substrates by (a) a modified solvothermal approach, (b) drop casting and slow crystallization processes and (c) unidirectional diffusion. Fig. 5(a) is reproduced with permission from ref. 112; Copyright 2015, American Chemical Society. Fig. 5(b) is reproduced with permission from ref. 113; Copyright 2018, Wiley. Fig. 5(c) is reproduced with permission from ref. 114; Copyright 2019, Elsevier.

oriented film growth on relevant substrates and improved capacitance could be potentially applicable in optoelectronics and energy storage devices.

Furthermore, we reported a strategic synthesis approach to fabricate self-standing and highly flexible covalent organic framework membranes (COFMs) with superior proton conductivity (Fig. 5(b)).¹¹³ This slow crystallization approach involves the reactions of amine-*p*-toluene sulfonic acid (PTSA·H₂O) salt

with a trialdehyde to synthesize three COF membranes, followed by the impregnation of PTSA·H₂O as a proton carrier within the COF pore. In brief, the diamines are homogeneously mixed with PTSA·H₂O and subsequently, the trialdehyde (Tp) was mixed. Then water was added to prepare a viscous slurry, which was cast into the molds of a glass substrate, followed by slow baking at 50–90 °C for 3–4 days. The impregnation of PTSA·H₂O within the COF pore provides



three COFMs PTSA@TpBD(Me)₂, PTSA@TpAzo and PTSA@TpBpy. The COFMs prepared by this method showed the highest reported proton conductivity amongst all porous crystalline polymeric materials. The membranes are operated under fuel cell proton exchange membrane operating conditions to confirm their practical utilization.

Unidirectional diffusion synthesis (UDS) is another technique to grow a COF layer on substrates at a liquid–liquid interface (Fig. 5(c)).¹¹⁴ The TpPa COF was grown on a polyvinylidene fluoride (PVDF) substrate at room temperature to prepare a COF-based composite membrane for efficient dye separation and water permeance. Immiscible solutions of an aldehyde (Tp) in hexane and an amine (Pa) in water were separately introduced into two sides of a diffusion cell. The Pa molecules pass through the PVDF membrane to react with the Tp aldehyde molecules at the interface, producing the TpPa COF layer on the PVDF substrate within 24 h of reaction. The composite membrane is highly efficient in dye separation. These techniques illustrate the versatility and challenges in fabricating COF thin films, highlighting the need for continued optimization to achieve high-quality, application-specific films.

2.2.3 Pristine films transferred onto substrates. COF thin films are typically synthesized through various interfacial crystallization processes conducted under ambient conditions, followed by their transfer to desired substrates for practical applications (Fig. 6(a)). Transferring these films requires meticulous handling to preserve their structural integrity, prevent crack formation, and ensure a strong attachment to the substrate. Several techniques have been reported for synthesizing COF thin films and their subsequent transfer onto different substrates. Interfacial polymerization, a well-established method for producing polymer thin films like polyamides and polyesters, has been effectively adapted to fabricate COF thin films.^{115–118} Two primary types of interfacial crystallization are commonly used: liquid/liquid and liquid/air. Our research group has developed a liquid/liquid interfacial crystallization approach to synthesize COF thin films, such as Tp-Bpy, Tp-Azo, Tp-Ttba, and Tp-Tta, at a dichloromethane/water interface at room temperature (Fig. 6(b)).¹¹⁹ In this method, amines from the aqueous layer diffuse into the dichloromethane layer containing the aldehyde, forming COF films at the interface. These thin films can be transferred onto various substrates, including polymer membranes, metallic wires, holey grids, and glass surfaces while maintaining their structural integrity. Films with larger pore diameters, like Tp-Bpy and Tp-Azo, were sandwiched between two macroporous polyester supports for molecular separation, utilizing optimized thicknesses of 2.1 μm and 5.3 μm , respectively.

Additionally, we have reported the synthesis of pristine COF thin films from covalent organic nanosheets (CONs), which are obtained by chemically exfoliating a 2D COF (DaTp).¹²¹ This process involves attaching *N*-hexylmaleimide molecules to the 9- and 10-positions of anthracene units in DaTp COF through a [4+2] cycloaddition reaction. The incorporation of *N*-hexylmaleimide disrupts the π – π interactions and the planarity of the COF layers, resulting in exfoliation and the

formation of CONs. These exfoliated CONs are then assembled into pristine DaTp-CON thin films at an air/water interface (Fig. 6(c)), which can be transferred to substrates like silicon wafers, glass slides, or even loops. Furthermore, photon-assisted synthesis has been utilized to create polyimine-based 2D COF thin films (pi-COF) on a water surface *via* Schiff-base condensation of terephthalaldehyde (PDA) and 1,3,5-tris(4-aminophenyl)-benzene (TAPB) (Fig. 6(d)).^{120,122} This method allows for the rapid (approximately 1 hour) and scalable synthesis of pi-COF films, with diameters of up to ~ 4 inches and precise control over the number of layers. The resulting films can be transferred to substrates such as silicon oxide, silicon, quartz, and mica, making them suitable for applications in field-effect transistors, sensors, and photodetector devices.


Surfactant-monolayer-assisted synthesis is another reported method for creating a few layers of crystalline polymer thin films on water surfaces at room temperature (Fig. 6(e)).¹²³ Surfactant monolayers, such as sodium (9Z)-octadec-9-en-1-yl sulfate, guide the arrangement and polymerization of monomers, forming 2D polyimide (2DPI) films. These films are synthesized by the condensation of isochromeno[4',5',6:6,5,10]anthra[2,1,9-*def*]isochromene-1,3,8,10-tetrone and 4,4',4'',4'''-(porphyrin-5,10,15,20-tetrayl)tetraaniline. The resulting thin films, with thicknesses of around 2 nm, can be transferred to substrates such as SiO₂/Si and holey copper grids for characterization. This suite of synthesis and transfer techniques underscore the versatility and adaptability of COF thin films, paving the way for their integration into a range of advanced applications.

2.2.4 Benefits and drawbacks of the synthesis methods. Interfacial crystallization processes can be conducted under ambient conditions, enabling the straightforward synthesis of free-standing thin films. However, these pristine films often need to be transferred onto various substrates for practical applications while maintaining their structural integrity and ensuring strong attachment to the supports (Fig. 7(a)). Achieving a robust film–substrate attachment and film integrity is challenging yet essential for fabricating electronic, electrochemical, and separation devices (Fig. 7(b)). *In situ* crystallization and the organized assembly of COF crystallites directly onto substrates are crucial to ensure optimal performance in such applications. Achieving high crystallinity, uniform film growth, and a smooth surface requires precise control over the reaction rate. This level of control is challenging in interfacial crystallization processes, where reactions occur rapidly at the interface. Controlling crystallization, managing film thickness, and transferring sub-10 nm COF thin films remain significant challenges when using interfacial methods. Furthermore, existing techniques for direct film growth on substrates often result in issues such as the deposition of bulk COF powders, inhomogeneous film coverage, rough surfaces, and inconsistent thickness.


The solvothermal process is the most effective approach for film growth on substrates. The simple and straightforward method is versatile for growing different types of thin films on various substrates. However, the method still suffers the prevailing challenge of thin film contamination with bulk




(a) Transferring pristine COF thin film on to a substrate:

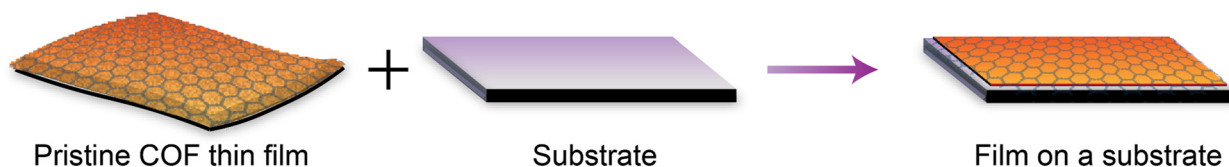


(b) Interfacial COF thin film synthesis:

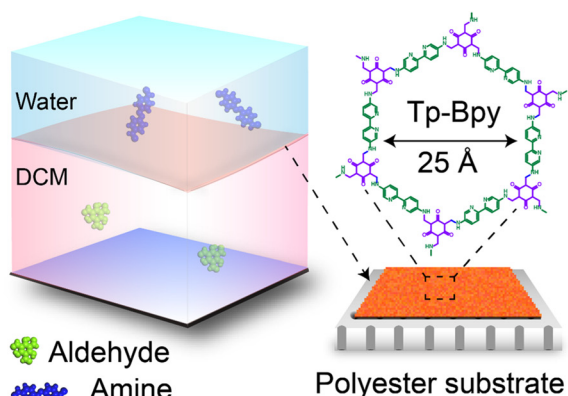

(c) CONs to COF thin film synthesis:

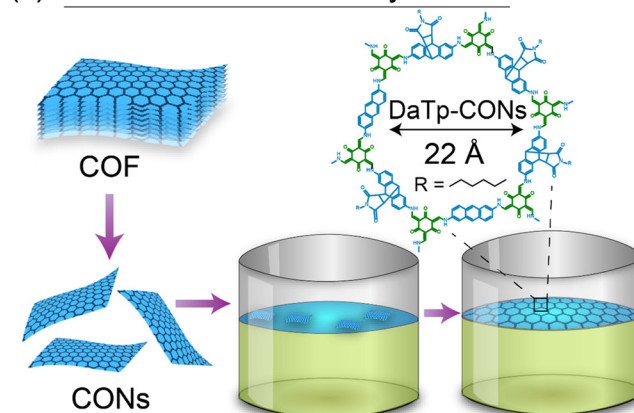

(d) COF thin films at air/liquid interface:

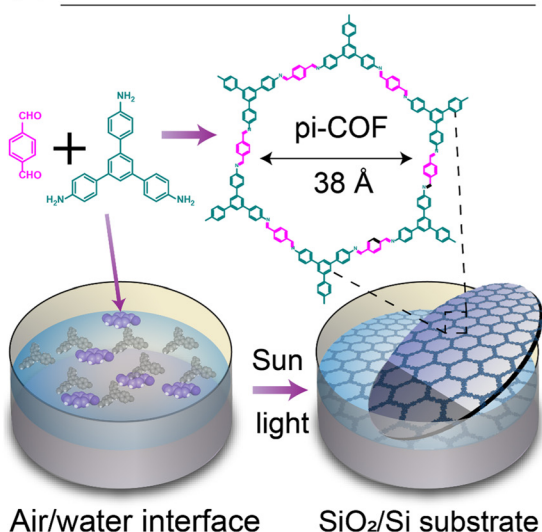

(e) Surfactant assisted synthesis:

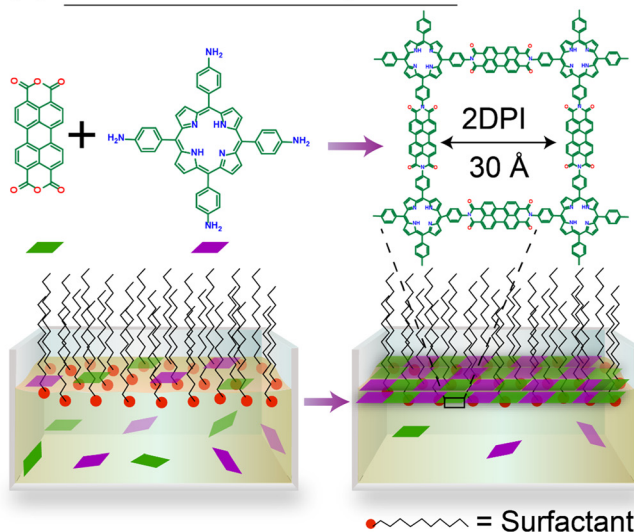



Fig. 6 Schematic representation of (a) transferring films onto supports, (b) interfacial synthesis of COF thin films then transferred to a polyester substrate, (c) synthesis of pristine COF films from CONs, (d) synthesis of pristine COF films at a liquid–air interface, and (e) surfactant assisted synthesis of crystalline polymer thin films. Fig. 6(b) is adapted with permission from ref. 26, Copyright 2021, American Chemical Society. Fig. 6(d) is adapted with permission from ref. 120, Copyright 2018, American Chemical Society.

powder as the method is dedicated to powdered COF synthesis. Furthermore, the vapor-assisted synthesis, solvent evaporation, and various solution casting methods are beneficial for thicker film synthesis and user-friendly, but the limitations of thinner and smooth film synthesis are yet to overcome. Rapid film synthesis by electrophoretic deposition demands the use of very high voltage (up to 900 V) and also this method is limited to conducting substrates.


Various modified approaches of the solvothermal process have been utilized to grow COF thin films on substrates and to avoid bulk powder contamination. For example, the synthesis of redox active DAQ-TFP oriented COF films involves a modified solvothermal approach using slow addition of one precursor solution to another.¹¹² This method produces oriented and crystalline COF films to access more redox active functional groups for enhanced areal capacitance over the randomly



(a) Synthesis of COF thin films:

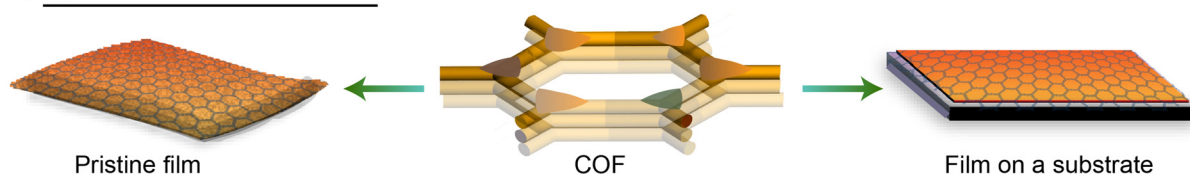

(b) Constraints with pristine thin films:

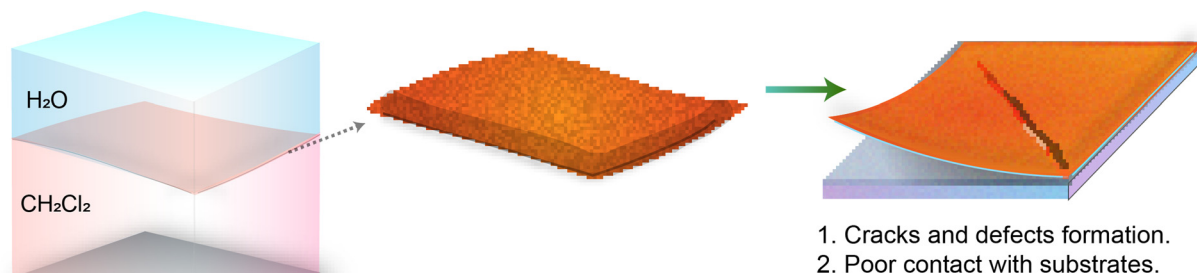

(c) Growth of COF thin films on substrates:

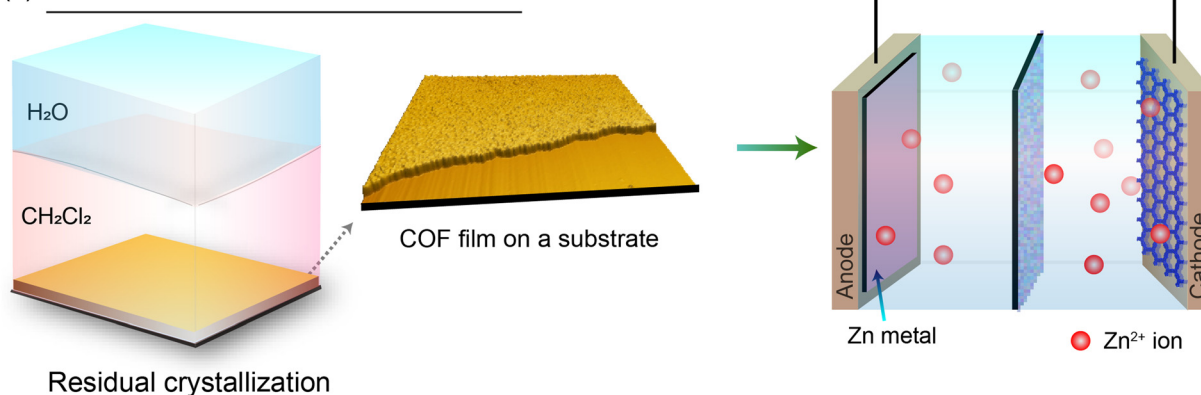


Fig. 7 Schematic representation of (a) COF thin film fabrication, (b) pristine COF film synthesis and the associated difficulties, and (c) COF thin film synthesis on substrates by residual crystallization.

oriented COF powder. However, it is difficult to completely avoid film contamination with powder using such a direct precursor mixing approach.

Furthermore, film thickness is also critical for applications in membrane separation and electronic devices. Thinner films can provide higher solvent flux, enhance separation performance, and increase conductivity. However, an optimal thickness is necessary to maintain the film's mechanical strength and uniformity. Thus, there is a pressing need to develop protocols for synthesizing high-quality thin films on various substrates, with stringent control over crystallization and thickness. We developed a unique concomitant crystallization methodology to address these challenges to synthesize large-area, continuous, and crack-free COF thin films on different supports. Our approach combines the benefits of interfacial crystallization and modified solvothermal synthesis, utilizing the interfacial crystallization process to initiate and regulate crystallization in a new method we call residual crystallization

(Fig. 7(c)). Conventional methods like solvothermal processes often lead to uncontrolled precursor mixing and precipitation without the interfacial crystallization component. However, the residual crystallization (RC) method enables the formation of smooth, homogeneous, and crack-free COF thin films with high crystallinity and permanent porosity on various substrates. Additionally, this method facilitates the fabrication of large-area sub-10 nm thin films.

It is crucial to incorporate these powders into other processes during film formation to prevent contamination from bulk COF powders. Our residual crystallization process effectively grows COF thin films on substrates with varying wettability, including metals, metal oxides, glass, silicon, ITO, and FTO. We observed superior film quality, particularly on hydrophilic substrates, with enhanced crystallinity and porosity for specific COFs. This advancement underscores the importance of substrate compatibility and precise control in synthesizing high-performance COF thin films (Table 1).





Table 1 Pros, cons and applications of COF growth on substrates by various synthesis methods

| COFs | Methods used | Advantages | Disadvantages | Stability | Surface area | Applications and potential uses | Ref. |
|---|---|--|---|--|---|--------------------------------------|---------|
| COF-5, TP-COF and NiPc-PBBA COF on SLG/Cu, SLG/SiO ₂ , and SLG/SiC | Solvothermal synthesis | Versatile for synthesis of different COF films Scalable technique | Thin film contamination with COF powder Not suitable for substrates sensitive to solvents and high temperature | | | Organic photovoltaic | 107,135 |
| HHTP-DPB COF on SLG/SiO ₂ | Solvothermal synthesis | Straightforward process Strong attachment with substrates | | | 930 m ² g ⁻¹ (powder) | Fluorescent sensors | 134 |
| BDT-COF on ITO-coated glass | Solvothermal synthesis | | | | 175 cm ² cm ⁻² | | 108 |
| TAPB-PDA on h-BN | Dynamic liquid/solid interfacial growth | Avoid film contamination Exceptional surface quality Adjustable thickness | Limited COF synthesis Complex reaction set-up | | | Optical applications | 136 |
| BDT-ETTA COF and BDT-ETTA COF/Pt on FTO coated glass | Electrophoretic deposition | Large-area films Very less synthesis time (2 min) | High electric voltage (up to 900 V) | | | Photoelectrochemical water reduction | 110 |
| BDT-COF and COF-5 on a glass substrate | Vapor-assisted conversion | Room temperature synthesis Beneficial for COF film synthesis using fragile precursors and on sensitive substrates | Difficult to synthesize thinner films Rough surface | | 990 m ² g ⁻¹ (BDT-COF film) | | 109 |
| TpBD(Me) ₂ , TpAzo and TpBpy | Solution casting | Self-standing COF film | Limited scope of COFs Difficult to synthesize thinner films Rough surface Monomer waste | | 2583–2933 m ² g ⁻¹ | Fuel cells | 113 |
| COF-5, DPB-COF, TP-COF and COF-10 on Pt QCM | Synthesis under continuous flow | Straightforward process Avoid film contamination Controlled thickness | | | | | 137 |
| TpAzo and TpDPP on glass, FTO, ITO, Si, and Cu | Residual crystallization | Avoid film contamination Controlled thickness Strong attachment Straightforward process | Long reaction time (4–5 days) | | 2093 and 1649 m ² g ⁻¹ on glass | | 26 |
| COF-BTDH with pectinase | Adsorption | | Weak interaction | | | Ginsenoside hydrolysis | 138 |
| COF1 with AChE | Adsorption | | Leaching | | | Sensing | 139 |
| Ni-TpBpy with enzymes (BGL, CBH and EG) and proteins (GFP and BG Rho) | Adsorption | High loading efficiency Generality | | Long-term stability of enzymes at room temperature | 58 m ² g ⁻¹ (BGL-COF) | Purification of enzymes and proteins | 33 |
| | | | | | 73 m ² g ⁻¹ (CBH-COF) 41 m ² g ⁻¹ (EG-COF) | Enzyme catalysis | |
| H-COF-OMe with laccase | Covalent linkage | Strong interactions | Limited to specialized functional groups Complex process | Enhanced pH, thermal, and storage stability | | Tetracycline degradation | 140 |
| MNPs@TTB-DHBD and Tz-Da with OPH ₂ GOx | Covalent linkage | Reusability Prevents enzyme leakage | | Improved stability | 549 m ² g ⁻¹ (d@Tz-Da@OPH) | Enzyme catalysis | 141 |

Table 1 (continued)

| COFs | Methods used | Advantages | Disadvantages | Stability | Surface area | Applications and potential uses | Ref. |
|--|------------------------------|---|---|--|--|---------------------------------|------|
| NKCOF-98 with lipase | <i>In situ</i> encapsulation | Straightforward approach | Limited reaction environments (like aqueous solution) | Improved stability | | | 142 |
| COF-42-B with Cyt c | Sacrificial templating | Large scale fabrication High loading Sufficient protection Confined microenvironment | Difficulty in COF synthesis | Stable at high temperature and in organic solvents | | | 143 |
| TpAzo and TpDPP with C ₁₀ FFVK assembly | Cladding | Excellent protection Prevents enzyme leakage High loading | COF cladding on enzymes is yet to be explored | Excellent stability in organic solvents | 708 & 504 m ² g ⁻¹ | Biocatalysis | 27 |

2.2.5 Applications of COF films on different substrates.

Fabricating COF thin films directly on specific substrates is essential for many practical applications. Films must be grown on current collectors for energy storage devices, while separation applications require thin films attached to porous supportive membranes. Additionally, the fabrication of thin-film transistors and other electronic devices relies on the deposition of films on glass or silicon-based substrates.

Renewable energy sources and storage devices are critical for sustaining modern society's technological demands. COF thin films, with their customizable redox-active functional groups and controlled thickness, have shown promise as electrode materials in energy storage devices like lithium-ion batteries, zinc-ion batteries, and supercapacitors. Quinone-based systems, such as those incorporating anthraquinone and hydroquinone units, have attracted significant interest. For example, an anthraquinone-based COF (DAAQ-ECOF) was mixed with conductive carbon black and a polyvinylidene fluoride binder in *N*-methyl-2-pyrrolidinone and drop-cast onto an alumina plate to form a cathode for lithium-ion batteries. Exfoliating the DAAQ COF to 3–5 nm thickness reduced the lithium-ion diffusion length, improving charge transfer and overall energy storage performance.¹²⁴ Hydroquinone-based COFs, such as HqTp COF, have also been used as cathodes for rechargeable aqueous zinc-ion batteries, where they are combined with conducting carbon nanofibers and a Nafion binder and coated onto modified carbon fiber paper (Fig. 8(a)).¹²⁵


COF thin films also act as separators in energy storage devices, using their ordered pore channels to block undesired molecules while allowing necessary ion transport. In sodium-sulfur (Na-S) batteries, azobenzene-functionalized COF films with dual-purpose narrow pores inhibit the polysulfide shuttle effect and provide sites for sodium ion migration, thereby extending the battery's lifespan and boosting capacity (Fig. 8(b)).¹²⁷

Furthermore, anthraquinone-based COFs have been employed as electrode materials for capacitors. DAAQ-BTA COF films were synthesized on 3D graphene using interfacial polymerization and subsequently attached to nickel foam as current collectors for electrochemical analysis.¹²⁸ We synthesized a redox active TpOME-DAQ COF having an interlayer hydrogen bonding structure as a free-standing supercapacitor electrode material (Fig. 8(c)).¹²⁶ The pristine COF membrane exhibited an excellent areal capacitance of 1600 mF cm⁻² with very high cycling stability of more than 10 000 cycles. The expected energy storage mechanism is attributed to both EDLC and pseudocapacitance due to its high porosity and redox active groups present in the backbone.


Li-metal and aqueous Zn-ion batteries face challenges such as dendrite growth, unstable solid-electrolyte interfaces (SEI), and electrolyte corrosion, leading to poor reversibility (Fig. 8(d)). COF thin films serve as effective protective layers, suppressing dendrite formation and minimizing undesirable reactions on metal anodes.¹²⁹ Due to their high mechanical strength, ordered pore channels, and controlled thickness, COF thin films facilitate ion transport while preventing dendrite




(a) Cathode material in zinc ion battery:

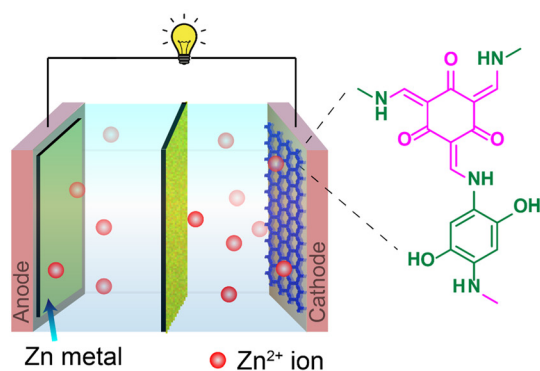


(b) COF thin film as active separators in battery:

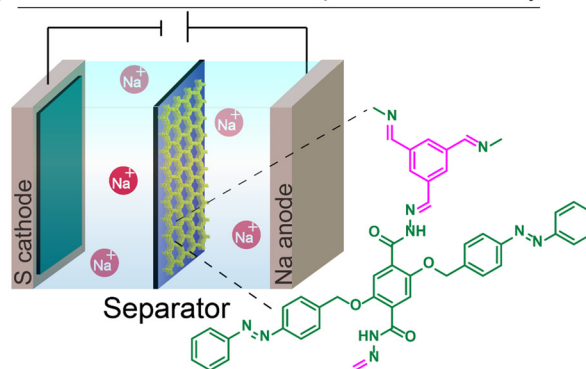


(c) Supercapacitor electrode material:

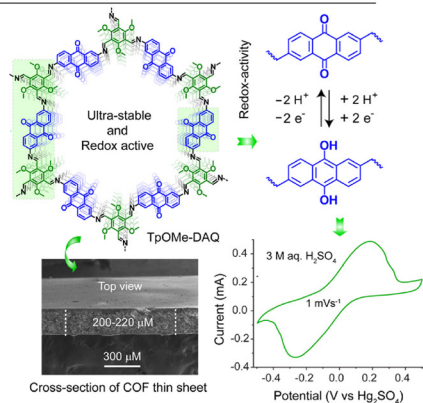

(d) Protective layer on Zn anode in battery:

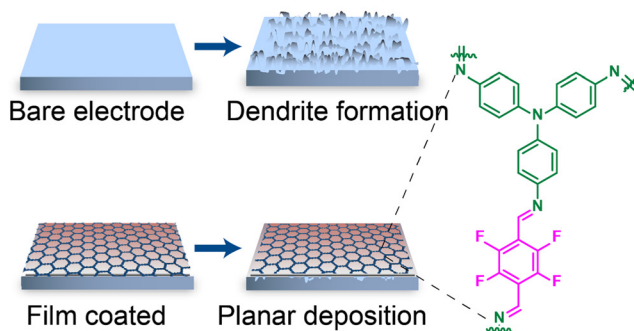

(e) Proton conducting membranes in fuel cells:

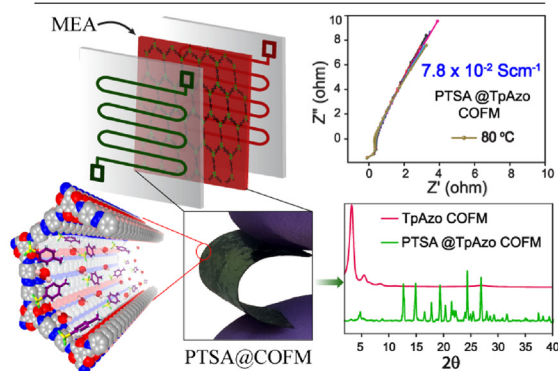

(f) Semiconducting layer in field-effect transistor:

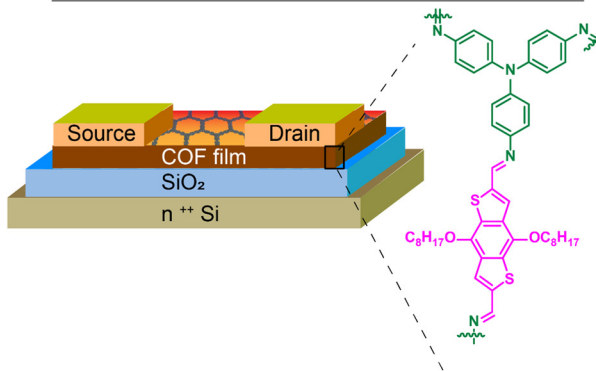


Fig. 8 Schematic representation of (a) a Zn-ion battery with a deposited COF layer as a cathode, (b) COF thin film as a separator in a battery, (c) COF membrane as a supercapacitor electrode material, (d) COF thin film as a protection layer for metal anodes in batteries, (e) flexible COF membranes for fuel cell applications and (f) field effect transistor with COF film as an active semiconducting layer. Fig. 8(c) is reproduced with permission from ref. 126; Copyright 2018, American Chemical Society. Fig. 8(e) is reproduced with permission from ref. 113; Copyright 2018, Wiley.

growth. For example, ultrathin fluorinated FCOF films have been used to protect zinc surfaces, improving corrosion resistance and enhancing ion transport through fluorine-containing pore channels.

Proton exchange membrane (PEM) fuel cells are a promising platform for clean power generation especially in transportation power systems. COFs with high proton conductivity, exceptional stability and desired functional groups have become the potential materials as proton exchange membranes in fuel cells. We have developed a synthetic strategy to prepare various

self-standing and flexible COF membranes (COFMs) with impregnated *p*-toluene sulfonic acid (PTSA-H₂O) as a proton carrier within COF pores (Fig. 8(e)).¹¹³ The COFMs exhibited highest proton conductivity of $7.8 \times 10^{-2} \text{ S cm}^{-1}$ compared to all other porous crystalline organic materials. Moreover, we tested their practical utilization under real PEM operating conditions and achieved the highest power density of 24 mW cm^{-2} amongst COFs and MOFs.

Field-effect transistors (FETs) are fundamental components of modern electronics, including amplifiers, sensors, memory



chips, and more. Smooth and homogeneous COF thin films are crucial for effective electronic connectivity between the substrate and the semiconductor layer. The polyTB COF thin film, with its imine-based conjugated structure, has demonstrated effectiveness as an active semiconducting layer in FETs (Fig. 8(f)). Previously reported boronate ester-based COFs, which require an edge-on orientation for charge transport, often pose fabrication challenges. In contrast, the polyTB COF thin film features in-plane charge transport with a highly smooth surface (an average roughness of 0.2 nm) and reduced thickness (1.8–29 nm), making it a strong candidate for semiconductor applications.¹³⁰ This film, synthesized at the solution/air interface, can be transferred onto silicon substrates for device fabrication.

COFs have been utilized as multifunctional materials for separation applications due to their intrinsic porous, crystalline structures with tunable pore size and structure, large surface area, tailored functionality and low density. COFs are not only utilized as continuous membranes but also as thin film nanocomposite and mixed matrix membranes. Randomly oriented amorphous polymer membranes lack ordered pore channels, uniform pore sizes and porosity, which creates difficulties in achieving high selectivity. The COF-based membranes are designed considering some crucial factors such as pore size, surface charge, wettability and stability for separation applications.

Gas separation is a promising application of COF-based membranes owing to their intrinsic porosity, high stability, and low transport resistance and adjustable pore size. A highly stable azine linked ACOF-1 membrane was grown on an aldehyde-modified Al_2O_3 support for CO_2/CH_4 gas separation.¹⁰⁵ The continuous COF membrane, with a narrow pore size of 0.94 nm, exhibits a high selectivity of 86.3 with a reasonable CO_2 permeance of $9.9 \times 10^{-9} \text{ mol}^{-2} \text{ s}^{-1} \text{ Pa}^{-1}$. The overall performance also exceeds the CO_2/CH_4 Robeson upper bound. The excellent performance is attributed to the high CO_2 adsorption capacity and very narrow pore diameter of the COF (Fig. 9(a)).

Furthermore, to overcome the difficulties in synthesizing COF membranes with a very narrow pore aperture close to the size of gas molecules, a bilayer COF membrane (COF-LZU1-ACOF-1) was synthesized on a dual-amino-functionalized Al_2O_3 substrate for H_2 separation from other gases.¹⁰⁶ A temperature-swing solvothermal process was utilized to grow the imine-based COF-LZU1 and ACOF-1 layers on the porous alumina substrate. The interlaced pore size of the COF-COF composite membrane (pore sizes of ~ 1.8 nm for COF-LZU1 and ~ 0.94 nm for ACOF1) is expected to be in the range of kinetic diameter of common gas molecules. The bilayer COF membrane exhibits a superior separation selectivity for H_2/CH_4 , H_2/CO_2 and H_2/N_2 gas mixtures compared to the individual COF membranes. The high separation performances of the COF-COF composite membrane exceed the Robeson upper bounds for the gas mixtures.

Membrane separation is an energy efficient, environment-friendly, and sustainable process producing for clean water.

Desalination and waste-water recycling require COF membranes with appropriate pore size, surface charge, and functional backbones for nanofiltration of salts, dyes, and various organic molecules.

Industrial wastewater is mostly contaminated with carcinogenic and hazardous organic dyes, which are difficult to remove because they are highly resistant to heat and light. To overcome this issue, we developed the interfacial crystallization process to synthesize COF thin films (Tp-Tta, TpTtba, TpBpy and Tp-Azo) for separation of various dyes.¹¹⁹ The COF films showed excellent dye rejection performances, with the Tp-Bpy film showing 94% (BB, brilliant blue-G), 80% (CR, Congo red), 97% (AF, acid fuchsin), and 98% (RH, rhodamine B) and the Tp-Azo film showing 90% (BB), 79% (CR), 99% (AF), and 99% (RH). Furthermore, Tp-Bpy exhibits selective separation for AF when subjected to a mixed feed of AF and *p*-nitrophenol (NP). These highly stable β -ketoenamine COFs demonstrate the dye rejection efficiency over five cycles.

Technologies based on seawater desalination and wastewater treatment demand membranes with high ion sieving performance. A negatively charged COF-based composite nanofiltration membrane (SCOF/PA) was synthesized with pendant sulfonic acid groups on the COF backbone.¹³² The membrane, with remarkable hydrophilicity and substantial negative zeta potential (-57 mV), showed an excellent rejection of Na_2SO_4 (99.6%), a high single salt selectivity ($\text{NaCl}/\text{Na}_2\text{SO}_4$) of 178.5 and precise mono/divalent ion separation with a selectivity of up to 312.6 for $\text{Cl}^-/\text{SO}_4^{2-}$ (Fig. 9(b)).

In the pharmaceutical and chemical industries, organic solvent nanofiltration (OSN) has gained significant attention for solvent recycling and purification. Such applications necessitate membranes with high stability and solvent resistance as they are exposed to organic solvents. Therefore, the COFs with β -ketoenamine, hydrazine and imine linkages are more preferable.

A β -ketoenamine-based COF (TFP-DHF) thin film was fabricated on a porous anodic aluminium oxide substrate using the Langmuir-Blodgett (LB) technique.¹⁰⁴ The membrane showed excellent permeabilities for polar and nonpolar organic solvents because of the very low membrane thickness of the four-unit-cell and the crystalline nature of the COF. The ordered pore channels in the crystalline COF membrane improved the permeability by 100 times compared to the amorphous membrane synthesized by the same process. This suggests that the crystallinity plays an important role in separation applications, which signifies the practical use of COF-based membranes over polymeric membranes. Furthermore, the membrane showed excellent dye rejection ability with a molecular-weight-cut-off of approximately 900 Da.

Another COF (TpPa) was constructed as a separation layer by interfacial polymerization on a polyimide (PI) substrate for enhanced solvent transport and selective molecular sieving. Excellent solvent resistance of the TpPa/PI membrane makes it appropriate for separation and purification of organic solvents. The membrane showed high performance in ethanol permeance (58.0 LMH/MPa), fast green FCF rejection (96.2%) and *n*-hexane permeance (102.0 LMH/MPa).¹³³



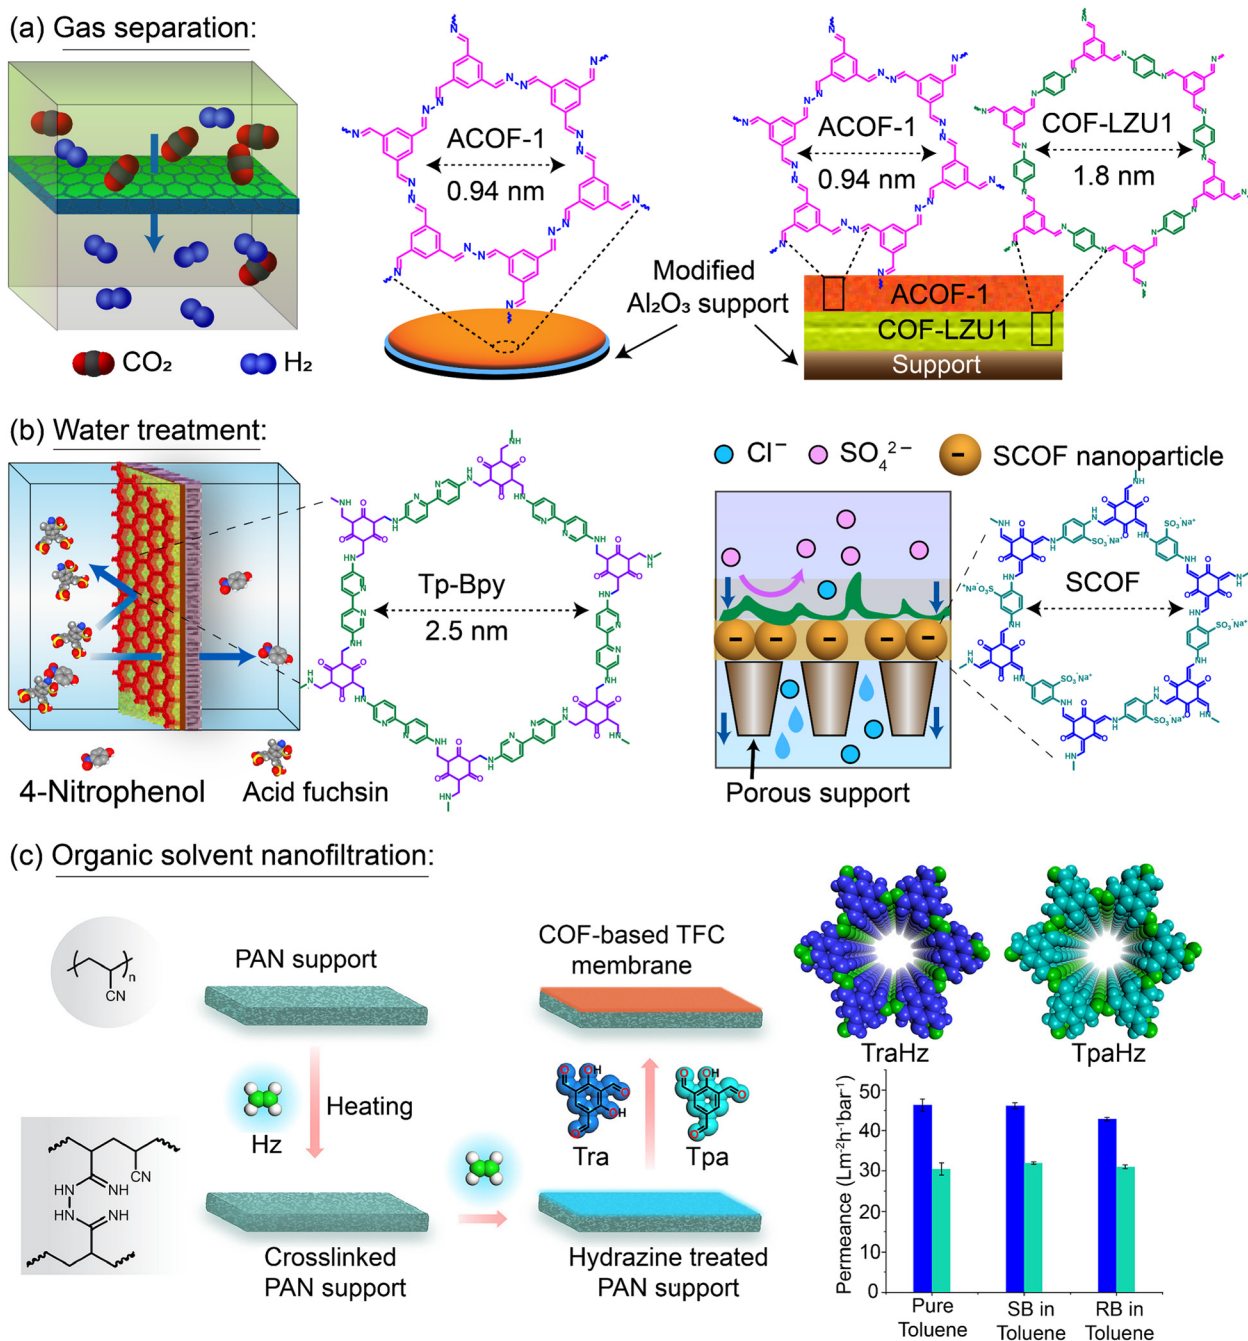


Fig. 9 Applications of COF-based membranes in (a) gas separation, (b) water treatment and (c) organic solvent nanofiltration. Fig. 9(c) is reproduced with permission from ref. 131; Copyright 2024, Elsevier.

Another example describes the synthesis of TraHz and TpaHz COF-based composite membranes by swift interfacial polymerization on a polyacrylonitrile (PAN) substrate.¹³¹ The highly stable membranes exhibit excellent separation performance even at higher temperatures in polar aprotic solvents (up to 80 °C). The membranes showed a molecular-weight cut-off of $\sim 650 \text{ g mol}^{-1}$ with an excellent dye rejection of more than 98% for the Chicago blue and Congo red dyes in THF, water, and ethanol. Also, the Rhodanile blue rejection is higher than 98% in toluene with remarkable permeances of 47 and


$33 \text{ L m}^{-2} \text{ h}^{-1} \text{ bar}^{-1}$ for toluene using TraHz-30 and TpaHz-30, respectively (Fig. 9(c)).

3. Future directions


Biocatalysts and biomimetic catalysts are known for their remarkable efficiency and selectivity in performing various organic transformations (Fig. 10(a)). However, their inherent fragility in non-aqueous media significantly limits their



(a) Biocatalysts and biomimetic-catalysts for organic transformations:

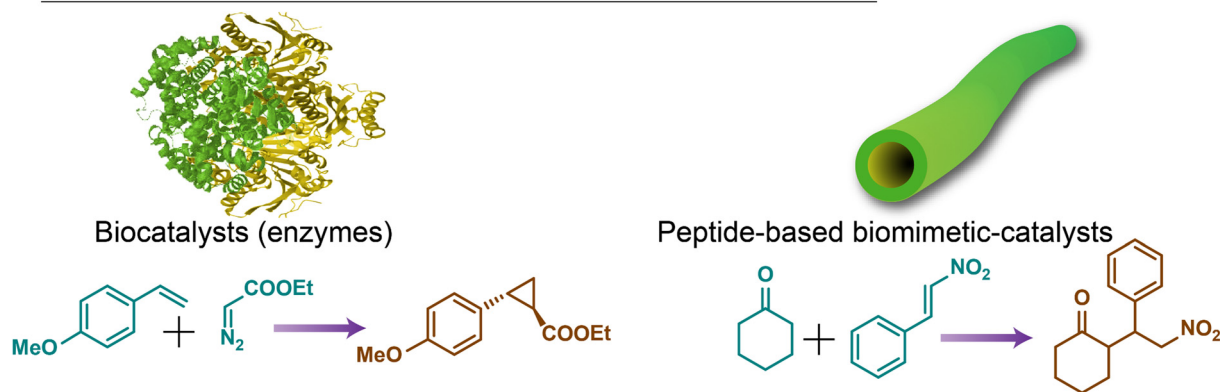

(b) Previous approaches of biocatalyst encapsulation:

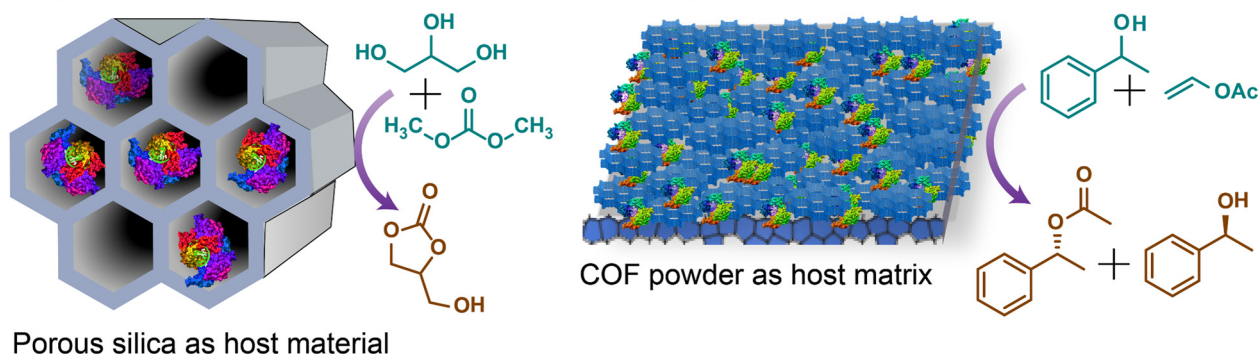

(c) COF cladding on biocatalysts:

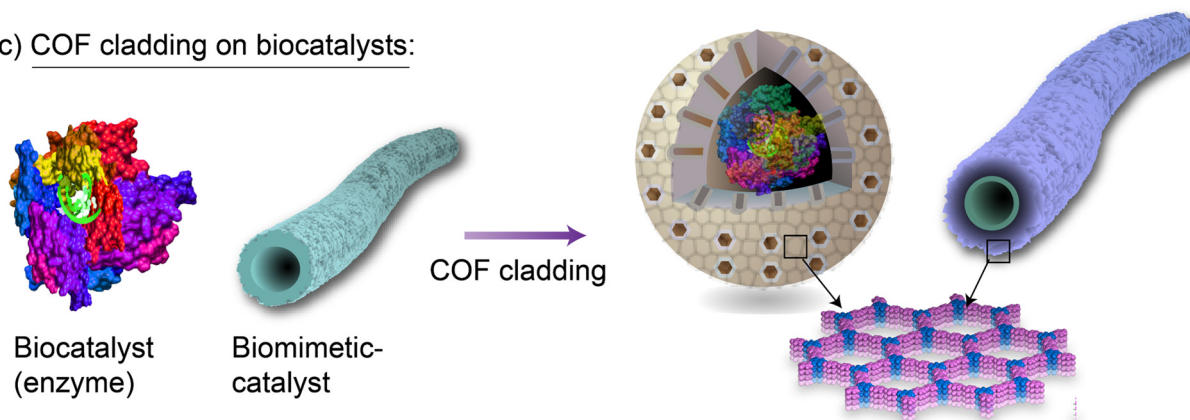


Fig. 10 Schematic representation of (a) biocatalysis with enzyme and biomimetic catalysts, (b) encapsulation of biocatalysts in porous matrices, and (c) cladding COF membranes on biocatalysts. Fig. 10(c) is adapted with permission from ref. 27; Copyright 2023, American Chemical Society.

industrial applicability. To address this challenge, researchers have explored porous, inert matrices to encapsulate biocatalysts, which has allowed for some degree of stabilization during reactions (Fig. 10(b)). Despite these advancements, such encapsulation methods—often based on noncovalent interactions—suffer from leaching and poor recyclability under operational conditions. A more sustainable and robust approach involves cladding or armouring biocatalysts with porous, crystalline membranes that feature well-defined pore channels. Similar to how a cell membrane facilitates the selective transport of molecules, ions, and metabolic products, COF membranes with precisely structured pores can provide

access to active sites for catalytic transformations while ensuring stability. These well-defined pore channels allow organic molecules to transit efficiently, thus preserving the catalytic activity of the biocatalysts. We recently developed a novel cladding technique to armour peptide-based biomimetic catalysts with COF membranes, enabling them to perform retro-aldol catalysis in various non-aqueous media, including acetone, acetonitrile, and dichloromethane. This approach demonstrates that COF cladding can offer structural protection and functional access, effectively stabilizing biocatalysts in environments where they typically degrade (Fig. 10(c)). We believe this method can be extended to enzyme-based



biocatalysts, using noncovalent interactions to armour them with COF membranes without compromising their structural integrity and catalytic functions. Such COF cladding represents a significant advancement in the field by stabilizing biocatalysts and preventing leaching in non-aqueous media. The ability to grow COF membranes directly on biological substrates holds immense potential for enabling various organic transformations in both aqueous and non-aqueous environments, thus broadening the industrial applicability of biocatalysts.

4. Conclusions and overview

This review emphasizes the critical role of substrate compatibility and innovative synthesis methods in successfully fabricating and applying covalent organic framework (COF) thin films. Directly growing COF thin films on suitable substrates is essential to ensure structural integrity, optimal performance, and strong film–substrate adhesion. The versatility of COF thin films, with properties such as high crystallinity, tunable pore sizes and customizable functional groups, has made them invaluable for separation processes, energy storage, and electronic and optoelectronic device applications. We have highlighted various strategies for synthesizing COF thin films on diverse substrates, including metals, metal oxides, glass, and polymers, and discussed the benefits and challenges associated with each method. This review also explores the critical parameters influencing film quality, such as reaction rate control, film thickness, and substrate compatibility, which are pivotal for advancing COF thin-film technologies. Moreover, developing a cladding technique to armour biocatalysts with COF membranes marks a significant breakthrough. This approach offers a sustainable solution to the instability of biocatalysts in non-aqueous environments, ensuring robust performance and preventing leaching while preserving the catalytic function. By extending the COF cladding technique to biological substrates, this method can revolutionize biocatalytic processes in both aqueous and non-aqueous media. This review provides a comprehensive understanding of COF thin film fabrication, highlighting innovative strategies to enhance film quality and functionality across various applications. The insights presented here pave the way for future research and development in COF thin films, offering tailored solutions for next-generation industrial and technological advancements.

Author contributions

Ashok Kumar Mahato: conceptualization, writing – original draft, writing – reviewing and editing; Satyadip Paul: global checking; and Rahul Banerjee: conceptualization, writing – reviewing and editing.

Data availability

No primary research results, software or code have been included and no new data were generated or analysed as part of this review.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

A. K. M. and S. P. acknowledge CSIR for Research fellowship. R. B. acknowledges SERB SUPRA (SPR/2021/000020) for funding.

References

- 1 A. W. Feinberg, A. Feigel, S. S. Shevkoplyas, S. Sheehy, G. M. Whitesides and K. K. Parker, *Science*, 2007, **317**, 1366–1370.
- 2 D. Gao, B. Li, Q. Liu, C. Zhang, Z. Yu, S. Li, J. Gong, L. Qian, F. Vanin, K. Schutt, M. A. Davis, A. F. Palmstrom, S. P. Harvey, N. J. Long, J. M. Luther, X. C. Zeng and Z. Zhu, *Science*, 2024, **386**, 187–192.
- 3 L. Ge, H. Song, J. Zhu, Y. Zhang, Z. Zhou and B. Van der Bruggen, *J. Mater. Chem. A*, 2024, **12**, 7975–8013.
- 4 A. Gumyusenge, D. T. Tran, X. Luo, G. M. Pitch, Y. Zhao, K. A. Jenkins, T. J. Dunn, A. L. Ayzner, B. M. Savoie and J. Mei, *Science*, 2018, **362**, 1131–1134.
- 5 K. Hikima, K. Shimizu, H. Kiuchi, Y. Hinuma, K. Suzuki, M. Hirayama, E. Matsubara and R. Kanno, *J. Am. Chem. Soc.*, 2022, **144**, 236–247.
- 6 X. Luo, M. Zhang, Y. Hu, Y. Xu, H. Zhou, Z. Xu, Y. Hao, S. Chen, S. Chen, Y. Luo, Y. Lin and J. Zhao, *Science*, 2024, **385**, 647–651.
- 7 M. Sandru, E. M. Sandru, W. F. Ingram, J. Deng, P. M. Stenstad, L. Deng and R. J. Spontak, *Science*, 2022, **376**, 90–94.
- 8 H. Tsai, F. Liu, S. Shrestha, K. Fernando, S. Tretiak, B. Scott, D. T. Vo, J. Strzalka and W. Nie, *Sci. Adv.*, 2020, **6**, eaay0815.
- 9 Z. Zhang, Y. Li, R. Xu, W. Zhou, Y. Li, S. T. Oyakhire, Y. Wu, J. Xu, H. Wang, Z. Yu, D. T. Boyle, W. Huang, Y. Ye, H. Chen, J. Wan, Z. Bao, W. Chiu and Y. Cui, *Science*, 2022, **375**, 66–70.
- 10 A. P. Côté, A. I. Benin, N. W. Ockwig, M. O'Keeffe, A. J. Matzger and O. M. Yaghi, *Science*, 2005, **310**, 1166–1170.
- 11 C. S. Diercks and O. M. Yaghi, *Science*, 2017, **355**, eaal1585; L. Ge, H. Song, J. Zhu, Y. Zhang, Z. Zhou and B. Van der Bruggen, *J. Mater. Chem. A*, 2024, **12**, 7975–8013.
- 12 K. Geng, T. He, R. Liu, S. Dalapati, K. T. Tan, Z. Li, S. Tao, Y. Gong, Q. Jiang and D. Jiang, *Chem. Rev.*, 2020, **120**, 8814–8933.
- 13 S. Kandambeth, K. Dey and R. Banerjee, *J. Am. Chem. Soc.*, 2019, **141**, 1807–1822.
- 14 P. Shao, J. Li, F. Chen, L. Ma, Q. Li, M. Zhang, J. Zhou, A. Yin, X. Feng and B. Wang, *Angew. Chem., Int. Ed.*, 2018, **57**, 16501–16505.
- 15 H. Wang, Z. Zeng, P. Xu, L. Li, G. Zeng, R. Xiao, Z. Tang, D. Huang, L. Tang, C. Lai, D. Jiang, Y. Liu, H. Yi, L. Qin,



- S. Ye, X. Ren and W. Tang, *Chem. Soc. Rev.*, 2019, **48**, 488–516.
- 16 X. Zhao, P. Pachfule and A. Thomas, *Chem. Soc. Rev.*, 2021, **50**, 6871–6913.
- 17 L. K. Beagle, Q. Fang, L. D. Tran, L. A. Baldwin, C. Muratore, J. Lou and N. R. Glavin, *Mater. Today*, 2021, **51**, 427–448.
- 18 S. Kandambeth, B. P. Biswal, H. D. Chaudhari, K. C. Rout, S. Kunjattu H, S. Mitra, S. Karak, A. Das, R. Mukherjee, U. K. Kharul and R. Banerjee, *Adv. Mater.*, 2017, **29**, 1603945.
- 19 H. S. Sasmal, A. Kumar Mahato, P. Majumder and R. Banerjee, *J. Am. Chem. Soc.*, 2022, **144**, 11482–11498.
- 20 S. Bag, H. S. Sasmal, S. P. Chaudhary, K. Dey, D. Blätte, R. Guntermann, Y. Zhang, M. Položij, A. Kuc, A. Shelke, R. K. Vijayaraghavan, T. G. Ajithkumar, S. Bhattacharyya, T. Heine, T. Bein and R. Banerjee, *J. Am. Chem. Soc.*, 2023, **145**, 1649–1659.
- 21 J. I. Feldblyum, C. H. McCreery, S. C. Andrews, T. Kurosawa, E. J. G. Santos, V. Duong, L. Fang, A. L. Ayzner and Z. Bao, *Chem. Commun.*, 2015, **51**, 13894–13897.
- 22 A. Gangopadhyay, B. J. Nablo, M. V. Rao and D. R. Reyes, *Adv. Eng. Mater.*, 2017, **19**, 1600592.
- 23 P. Sarkar, C. Wu, Z. Yang and C. Y. Tang, *Chem. Soc. Rev.*, 2024, **53**, 4374–4399.
- 24 H. Wang, B. He, F. Liu, C. Stevens, M. A. Brady, S. Cai, C. Wang, T. P. Russell, T.-W. Tan and Y. Liu, *J. Mater. Chem. C*, 2017, **5**, 5090–5095.
- 25 D. Hou, G. Dai, J. Wang, H. Fan, L. Zhang and Z. Luan, *Sep. Purif. Technol.*, 2012, **101**, 1–10.
- 26 A. Kumar Mahato, S. Bag, H. S. Sasmal, K. Dey, I. Giri, M. Linares-Moreau, C. Carbonell, P. Falcato, E. B. Gowd, R. K. Vijayaraghavan and R. Banerjee, *J. Am. Chem. Soc.*, 2021, **143**, 20916–20926.
- 27 A. Kumar Mahato, S. Pal, K. Dey, A. Reja, S. Paul, A. Shelke, T. G. Ajithkumar, D. Das and R. Banerjee, *J. Am. Chem. Soc.*, 2023, **145**, 12793–12801.
- 28 S. Hameed, A. Hayat, E. A. Alghamdi, N. Bano, F. Jubeen and A. A. Khurram, *J. Sci.: Adv. Mater. Devices*, 2023, **8**, 100632.
- 29 Y. Jin, Y. Hu, M. Ortiz, S. Huang, Y. Ge and W. Zhang, *Chem. Soc. Rev.*, 2020, **49**, 4637–4666.
- 30 X. Fan, S. Zhai, S. Xue and L. Zhi, *ACS Appl. Mater. Interfaces*, 2024, **16**, 40371–40390.
- 31 R. Gao, X. Kou, S. Huang, G. Chen and G. Ouyang, *Chem-BioChem*, 2024, **25**, e202400339.
- 32 S. Paul, M. Gupta, K. Dey, A. K. Mahato, S. Bag, A. Torris, E. B. Gowd, H. Sajid, M. A. Addicoat, S. Datta and R. Banerjee, *Chem. Sci.*, 2023, **14**, 6643–6653.
- 33 S. Paul, M. Gupta, A. Kumar Mahato, S. Karak, A. Basak, S. Datta and R. Banerjee, *J. Am. Chem. Soc.*, 2024, **146**, 858–867.
- 34 D. Zheng, Y. Zheng, J. Tan, Z. Zhang, H. Huang and Y. Chen, *Nat. Commun.*, 2024, **15**, 5510.
- 35 Q. Zhu, Y. Zheng, Z. Zhang and Y. Chen, *Nat. Protoc.*, 2023, **18**, 3080–3125.
- 36 H. Yan, X. Miao, J. Xu, G. Pan, Y. Zhang, Y. Shi, M. Guo and Y. Liu, *J. Membr. Sci.*, 2015, **475**, 504–510.
- 37 J. Li, J.-L. Gong, G.-M. Zeng, B. Song, W.-C. Cao, S.-Y. Fang, S.-Q. Tang, Y. Guan, Z.-K. Tan, Z.-P. Chen, X.-Q. Mao and R.-L. Zhu, *Sep. Purif. Technol.*, 2021, **276**, 119352.
- 38 S. Peng, Y.-X. Fang, Z.-L. Xu, R. Jia, R. Han, L. Yu and S.-J. Xu, *Sep. Purif. Technol.*, 2025, **355**, 129633.
- 39 H. Herman, R. C. T. Slade and J. R. Varcoe, *J. Membr. Sci.*, 2003, **218**, 147–163.
- 40 A. A. Oun, G. H. Shin, J.-W. Rhim and J. T. Kim, *Food Packag. Shelf Life*, 2022, **34**, 100991.
- 41 N. Zhang, Z. Huang, N. Yang, L. Zhang, B. Jiang, Y. Sun and J. Ma, *Sep. Purif. Technol.*, 2020, **232**, 115964.
- 42 Y. Lu, Z. Wang, W. Fang, Y. Zhu, Y. Zhang and J. Jin, *Ind. Eng. Chem. Res.*, 2020, **59**, 22533–22540.
- 43 D. C. Borrelli, S. Lee and K. K. Gleason, *J. Mater. Chem. C*, 2014, **2**, 7223–7231.
- 44 M.-K. Dai, J.-T. Lian, T.-Y. Lin, M.-C. Chen, Y. Tai and Y.-F. Chen, *Org. Electron.*, 2012, **13**, 2229–2234.
- 45 P. Liu, Y. Wu, H. Pan, B. S. Ong and S. Zhu, *Macromolecules*, 2010, **43**, 6368–6373.
- 46 M.-T. Lee, J.-K. Chang, Y.-T. Hsieh, W.-T. Tsai and C.-K. Lin, *J. Solid State Electrochem.*, 2010, **14**, 1697–1703.
- 47 M. Nakayama, A. Tanaka, Y. Sato, T. Tonosaki and K. Ogura, *Langmuir*, 2005, **21**, 5907–5913.
- 48 M. S. Çögenli, S. Mukerjee and A. B. Yurtcan, *Fuel Cells*, 2015, **15**, 288–297.
- 49 S. Cuynet, A. Caillard, T. Lecas, J. Bigarré, P. Buvat and P. Brault, *J. Phys. D: Appl. Phys.*, 2014, **47**, 272001.
- 50 M. M. Rahman, K. Inaba, G. Batnagyt, M. Saikawa, Y. Kato, R. Awata, B. Delgertsetsega, Y. Kaneta, K. Higashi, T. Uruga, Y. Iwasawa, K. Ui and T. Takeguchi, *RSC Adv.*, 2021, **11**, 20601–20611.
- 51 Y.-J. Wang, N. Zhao, B. Fang, H. Li, X. T. Bi and H. Wang, *Chem. Rev.*, 2015, **115**, 3433–3467.
- 52 K. Liang, Y. Wang, S. Shao, M. Luo, V. Pecunia, L. Shao, J. Zhao, Z. Chen, L. Mo and Z. Cui, *J. Mater. Chem. C*, 2019, **7**, 6169–6177.
- 53 B. K. Yap, Z. Zhang, G. S. H. Thien, K.-Y. Chan and C. Y. Tan, *Appl. Surf. Sci.*, 2023, **16**, 100423.
- 54 Z. Chen, D. Han, X. Zhang and Y. Wang, *Sci. Rep.*, 2019, **9**, 17175.
- 55 Y. Zhao, Z. Wang, G. Xu, L. Cai, T.-H. Han, A. Zhang, Q. Wu, R. Wang, T. Huang, P. Cheng, S.-Y. Chang, D. Bao, Z. Zhao, M. Wang, Y. Huang and Y. Yang, *Adv. Funct. Mater.*, 2020, **30**, 2003285.
- 56 Y. Zhu, Y. He, S. Jiang, L. Zhu, C. Chen and Q. Wan, *J. Semicond.*, 2021, **42**, 031101.
- 57 J. Park, S. Go, W. Chae, C. I. Ryoo, C. Kim, H. Noh, S. Kim, B. Du Ahn, I.-T. Cho, P. S. Yun, J. U. Bae, Y. S. Park, S. Kim and D. H. Kim, *Sci. Rep.*, 2024, **14**, 10067.
- 58 Y. Shin, S. T. Kim, K. Kim, M. Y. Kim, S. Oh and J. K. Jeong, *Sci. Rep.*, 2017, **7**, 10885.
- 59 K. Banerjee, A. Roy, S. Ghosh, H. R. Inta, A. Mondal, S. Ghosh, A. Mitra, A. K. Mahato and V. Mahalingam, *ACS Appl. Energy Mater.*, 2024, **7**, 7745–7758.
- 60 G. Fang, J. Zhou, A. Pan and S. Liang, *ACS Energy Lett.*, 2018, **3**, 2480–2501.



- 61 X. Jia, C. Liu, Z. G. Neale, J. Yang and G. Cao, *Chem. Rev.*, 2020, **120**, 7795–7866.
- 62 A. Khayum M, M. Ghosh, V. Vijayakumar, A. Halder, M. Nurhuda, S. Kumar, M. Addicoat, S. Kurungot and R. Banerjee, *Chem. Sci.*, 2019, **10**, 8889–8894.
- 63 W. Kim, C. Hwang, Y. M. Kim, J.-S. Yu, Y.-J. Kim, K. J. Kim and H.-S. Kim, *J. Mater. Chem. A*, 2024, **12**, 14786–14791.
- 64 A. Manthiram, *ACS Cent. Sci.*, 2017, **3**, 1063–1069.
- 65 A. Mondal, H. R. Inta, A. Roy, A. Kumar Mahato and V. Mahalingam, *ACS Appl. Nano Mater.*, 2023, **6**, 12040–12049.
- 66 G. Tudu, S. Ghosh, H. R. Inta, H. V. S. R. M. Koppiseti, S. Ganguli, A. K. Mahato and V. Mahalingam, *ChemNanoMat*, 2022, **8**, e202200199.
- 67 P. Vanaphuti, K. Scanlan and A. Manthiram, *RSC Sustainability*, 2024, **2**, 1969–1978.
- 68 B. Zhang, X. Wang, S. Wang, Y. Li, L. Chen, H. Jiao, Z. Yu and J. Tu, *J. Energy Chem.*, 2025, **100**, 1–17.
- 69 Z. Duan, Y. Wu, J. Lin, L. Wang and D.-L. Peng, *Energies*, 2022, **15**, 8980.
- 70 A. O'Donoghue, M. Shine, I. M. Povey and J. F. Rohan, *Int. J. Mol. Sci.*, 2023, **24**, 11207.
- 71 N. An, F. Zhang, Z. Hu, Z. Li, L. Li, Y. Yang, B. Guo and Z. Lei, *RSC Adv.*, 2015, **5**, 23942–23951.
- 72 N. J. Hestand and F. C. Spano, *Acc. Chem. Res.*, 2017, **50**, 341–350.
- 73 T.-H. Chao, M.-J. Chang, M. Watanabe, M.-H. Luo, Y. J. Chang, T.-C. Fang, K.-Y. Chen and T. J. Chow, *Chem. Commun.*, 2012, **48**, 6148–6150.
- 74 R. A. Jonson, V. S. Battaglia and M. C. Tucker, *ACS Appl. Energy Mater.*, 2023, **6**, 745–752.
- 75 E. J. Son, J. H. Kim, K. Kim and C. B. Park, *J. Mater. Chem. A*, 2016, **4**, 11179–11202.
- 76 N. An, F. Zhang, Z. Hu, Z. Li, L. Li, Y. Yang, B. Guo and Z. Lei, *RSC Adv.*, 2015, **5**, 23942–23951.
- 77 K. M. Blackwood, *Science*, 1996, **273**, 909–912.
- 78 A. K. Rylski, H. L. Cater, K. S. Mason, M. J. Allen, A. J. Arrowood, B. D. Freeman, G. E. Sanoja and Z. A. Page, *Science*, 2022, **378**, 211–215.
- 79 Y. Zhang, K. Zhou, S. Su, J. Gao, J. Liu and L. Jiang, *Sci. Adv.*, 2024, **10**, eadm9620.
- 80 J. Liu, G. Han, D. Zhao, K. Lu, J. Gao and T.-S. Chung, *Sci. Adv.*, 2020, **6**, eabb1110.
- 81 Q.-W. Meng, S. Wu, M. Liu, Q. Guo, W. Xian, X. Zuo, S. Wang, H. Yin, S. Ma and Q. Sun, *Sci. Adv.*, 2023, **9**, eadh0207.
- 82 Q. Zhang, S. Dong, P. Shao, Y. Zhu, Z. Mu, D. Sheng, T. Zhang, X. Jiang, R. Shao, Z. Ren, J. Xie, X. Feng and B. Wang, *Science*, 2022, **378**, 181–186.
- 83 E. Zhou, X. Zhang, L. Zhu, E. Chai, J. Chen, J. Li, D. Yuan, L. Kang, Q. Sun and Y. Wang, *Sci. Adv.*, 2024, **10**, eadk8564.
- 84 X. Wang, M. Liu, Y. Liu, S. Shang, C. Du, J. Hong, W. Gao, C. Hua, H. Xu, Z. You, J. Chen and Y. Liu, *J. Am. Chem. Soc.*, 2023, **145**, 26900–26907.
- 85 D. Zhu, Y. Zhu, Y. Chen, Q. Yan, H. Wu, C.-Y. Liu, X. Wang, L. B. Alemany, G. Gao, T. P. Senftle, Y. Peng, X. Wu and R. Verduzco, *Nat. Commun.*, 2023, **14**, 2865.
- 86 C. R. DeBlase, K. E. Silberstein, T.-T. Truong, H. D. Abruña and W. R. Dichtel, *J. Am. Chem. Soc.*, 2013, **135**, 16821–16824.
- 87 L. K. Beagle, Q. Fang, L. D. Tran, L. A. Baldwin, C. Muratore, J. Lou and N. R. Glavin, *Mater. Today*, 2021, **51**, 427–448.
- 88 J. Fan, Z. Wang, H. Cheng, D. Wang and A. T. Wee, *Electron. Mater.*, 2023, **4**, 49–61.
- 89 I. Gadwal, G. Sheng, R. L. Thankamony, Y. Liu, H. Li and Z. Lai, *ACS Appl. Mater. Interfaces*, 2018, **10**, 12295–12299.
- 90 T. Kim, J. Oh, S. C. Kim, J.-G. Ahn, S. Kim, Y. Y. Kim and H. Lim, *Small Methods*, 2024, 2400063.
- 91 S. Park, Z. Liao, B. Ibarlucea, H. Qi, H.-H. Lin, D. Becker, J. Melidonie, T. Zhang, H. Sahabudeen, L. Baraban, C.-K. Baek, Z. Zheng, E. Zschech, A. Fery, T. Heine, U. Kaiser, G. Cuniberti, R. Dong and X. Feng, *Angew. Chem., Int. Ed.*, 2020, **59**, 8218–8224.
- 92 D. B. Shinde, L. Cao, A. D. D. Wananke, X. Li, S. Kumar, X. Liu, M. N. Hedhili, A.-H. Emwas, M. Addicoat, K.-W. Huang and Z. Lai, *Chem. Sci.*, 2020, **11**, 5434–5440.
- 93 L. A. Baldwin, J. W. Crowe, D. A. Pyles and P. L. McGrier, *J. Am. Chem. Soc.*, 2016, **138**, 15134–15137.
- 94 G. Chen, T. Wang, G. Zhang, G. Liu and W. Jin, *Adv. Membr.*, 2022, **2**, 100025.
- 95 C. Gong, H. Wang, G. Sheng, X. Wang, X. Xu, J. Wang, X. Miao, Y. Liu, Y. Zhang, F. Dai, L. Chen, N. Li, G. Xu, J. Jia, Y. Zhu and Y. Peng, *Angew. Chem., Int. Ed.*, 2022, **61**, e202204899.
- 96 B. Gui, X. Liu, Y. Cheng, Y. Zhang, P. Chen, M. He, J. Sun and C. Wang, *Angew. Chem., Int. Ed.*, 2022, **61**, e202113852.
- 97 G. Lin, H. Ding, D. Yuan, B. Wang and C. Wang, *J. Am. Chem. Soc.*, 2016, **138**, 3302–3305.
- 98 Y. Qu, Y. Liu, H. Jia, S. Xu, M. Zhang, T. Xiao and X. Du, *J. Environ. Chem. Eng.*, 2024, **12**, 112711.
- 99 K. Sheng, J. Zhu, L. Ge, J. Du, T. Luo, L. Jiang, W. Jing, S.-P. Sun, Y. Zhang and B. Van der Bruggen, *Adv. Membr.*, 2024, **4**, 100109.
- 100 Z. Chen, J. Wang, M. Hao, Y. Xie, X. Liu, H. Yang, G. I. N. Waterhouse, X. Wang and S. Ma, *Nat. Commun.*, 2023, **14**, 1106.
- 101 A. Jati, A. K. Mahato, D. Chanda, P. Kumar, R. Banerjee and B. Maji, *J. Am. Chem. Soc.*, 2024, **146**, 23923–23932.
- 102 T. Skorjanc, D. Shetty, M. E. Mahmoud, F. Gándara, J. I. Martinez, A. K. Mohammed, S. Boutros, A. Merhi, E. O. Shehayeb, C. A. Sharabati, P. Damacet, J. Raya, S. Gardonio, M. Hmadeh, B. R. Kaafarani and A. Trabolsi, *ACS Appl. Mater. Interfaces*, 2022, **14**, 2015–2022.
- 103 L. Stegbauer, K. Schwinghammer and B. V. Lotsch, *Chem. Sci.*, 2014, **5**, 2789–2793.
- 104 D. B. Shinde, G. Sheng, X. Li, M. Ostwal, A. H. Emwas, K. W. Huang and Z. Lai, *J. Am. Chem. Soc.*, 2018, **140**, 14342–14349.
- 105 H. Fan, A. Mundstock, J. Gu, H. Meng and J. Caro, *J. Mater. Chem. A*, 2018, **6**, 16849.
- 106 H. Fan, A. Mundstock, A. Feldhoff, A. Knebel, J. Gu, H. Meng and J. Caro, *J. Am. Chem. Soc.*, 2018, **140**, 10094–10098.



- 107 J. W. Colson, A. R. Woll, A. Mukherjee, M. P. Levendorf, E. L. Spitler, V. B. Shields, M. G. Spencer, J. Park and W. R. Dichtel, *Science*, 2011, **332**, 228–231.
- 108 D. D. Medina, V. Werner, F. Auras, R. Tautz, M. Dogru, J. Schuster, S. Linke, M. Döblinger, J. Feldmann, P. Knochel and T. Bein, *ACS Nano*, 2014, **8**, 4042–4052.
- 109 D. D. Medina, J. M. Rotter, Y. Hu, M. Dogru, V. Werner, F. Auras, J. T. Markiewicz, P. Knochel and T. Bein, *J. Am. Chem. Soc.*, 2015, **137**, 1016–1019.
- 110 J. M. Rotter, S. Weinberger, J. Kampmann, T. Sick, M. Shalom, T. Bein and D. D. Medina, *Chem. Mater.*, 2019, **31**, 10008–10016.
- 111 B. J. Smith, L. R. Parent, A. C. Overholts, P. A. Beaucage, R. P. Bisbey, A. D. Chavez, N. Hwang, C. Park, A. M. Evans, N. C. Gianneschi and W. R. Dichtel, *ACS Cent. Sci.*, 2017, **3**, 58–65.
- 112 C. R. DeBlase, K. Hernandez-Burgos, K. E. Silberstein, G. G. R. Guez-Calero, R. P. Bisbey, H. D. Abruna and W. R. Dichtel, *ACS Nano*, 2015, **9**(3), 3178–3183.
- 113 H. S. Sasmal, H. B. Aiyappa, S. N. Bhange, S. Karak, A. Halder, S. Kurungot and R. Banerjee, *Angew. Chem., Int. Ed.*, 2018, **57**(34), 10894–10898.
- 114 R. Wang, X. Shi, Z. Zhang, A. Xiao, S. Sun, Z. Cui and Y. Wang, *J. Membr. Sci.*, 2019, **586**, 274–280.
- 115 S. Karan, Z. Jiang and A. G. Livingston, *Science*, 2015, **348**, 1347–1351.
- 116 F. Radmanesh, A. Tena, E. J. R. Sudhölter, M. A. Hempenius and N. E. Benes, *ACS Appl. Polym. Mater.*, 2023, **5**, 1955–1964.
- 117 Y. Song, J.-B. Fan and S. Wang, *Mater. Chem. Front.*, 2017, **1**, 1028–1040.
- 118 F. Zhang, J.-b Fan and S. Wang, *Angew. Chem., Int. Ed.*, 2020, **59**, 21840–21856.
- 119 K. Dey, M. Pal, K. C. Rout, S. Kunjattu H, A. Das, R. Mukherjee, U. K. Kharul and R. Banerjee, *J. Am. Chem. Soc.*, 2017, **139**, 13083–13091.
- 120 S. Kim, H. Lim, J. Lee and H. C. Choi, *Langmuir*, 2018, **34**, 8731–8738.
- 121 M. A. Khayum, S. Kandambeth, S. Mitra, S. B. Nair, A. Das, S. S. Nagane, R. Mukherjee and R. Banerjee, *Angew. Chem., Int. Ed.*, 2016, **55**, 15604–15608.
- 122 F. Shao, W. Dai, Y. Zhang, W. Zhang, A. D. Schlüter and R. Zenobi, *ACS Nano*, 2018, **12**(5), 5021–5029.
- 123 K. Liu, H. Qi, R. Dong, R. Shivhare, M. Addicoat, T. Zhang, H. Sahabudeen, T. Heine, S. Mannsfeld, U. Kaiser, Z. Zheng and X. Feng, *Nat. Chem.*, 2019, **11**, 994–1000.
- 124 S. Wang, Q. Wang, P. Shao, Y. Han, X. Gao, L. Ma, S. Yuan, X. Ma, J. Zhou, X. Feng and B. Wang, *J. Am. Chem. Soc.*, 2017, **139**, 4258–4261.
- 125 A. Khayum M, M. Ghosh, V. Vijayakumar, A. Halder, M. Nurhuda, S. Kumar, M. Addicoat, S. Kurungot and R. Banerjee, *Chem. Sci.*, 2019, **10**, 8889–8894.
- 126 A. Halder, M. Ghosh, A. Khayum M, S. Bera, M. Addicoat, H. S. Sasmal, S. Karak, S. Kurungot and R. Banerjee, *J. Am. Chem. Soc.*, 2018, **140**, 10941–10945.
- 127 C. Yin, Z. Li, D. Zhao, J. Yang, Y. Zhang, Y. Du and Y. Wang, *ACS Nano*, 2022, **16**, 14178–14187.
- 128 Z. Zha, L. Xu, Z. Wang, X. Li, Q. Pan, P. Hu and S. Lei, *ACS Appl. Mater. Interfaces*, 2015, **7**, 17837–17843.
- 129 Z. Zhao, R. Wang, C. Peng, W. Chen, T. Wu, B. Hu, W. Weng, Y. Yao, J. Zeng, Z. Chen, P. Liu, Y. Liu, G. Li, J. Guo, H. Lu and Z. Guo, *Nat. Commun.*, 2021, **12**, 6606.
- 130 J. I. Feldblyum, C. H. McCreery, S. C. Andrews, T. Kurosawa, E. J. G. Santos, V. Duong, L. Fang, A. L. Ayzner and Z. Bao, *Chem. Commun.*, 2015, **51**, 13894–13897.
- 131 S. Kumar, N. Alqadhi, J. Hu and G. Szekely, *J. Membr. Sci.*, 2024, **691**, 122257.
- 132 S. Xua, H. Lina, G. Lia, J. Wang, Q. Hana and F. Liu, *Chem. Eng. J.*, 2022, **427**, 132009.
- 133 F. Xu, S. Zhao, J. Song, Y. Peng and B. Su, *Membranes*, 2024, **14**, 234.
- 134 E. L. Spitler, B. T. Koo, J. L. Novotney, J. W. Colson, F. J. Uribe-Romo, G. D. Gutierrez, P. Clancy and W. R. Dichtel, *J. Am. Chem. Soc.*, 2011, **133**, 19416–19421.
- 135 C. Poelking, M. Tietze, C. Elschner, S. Olthof, D. Hertel, B. Baumeier, F. Wurthner, K. Meerholz, K. Leo and D. Andrienko, *Nat. Mater.*, 2015, **14**, 434–439.
- 136 T. Kim, J. Oh, S. C. Kim, J. Ahn, S. Kim, Y. Y. Kim and H. Lim, *Small Methods*, 2024, **8**, 2400063.
- 137 R. P. Bisbey, C. R. DeBlase, B. J. Smith and W. R. Dichtel, *J. Am. Chem. Soc.*, 2016, **138**(36), 11433–11436.
- 138 H. Cheng, Y. Wei, J. Han, X. Wang, W. Ji and X. Jin, *Process Biochem.*, 2022, **118**, 317–322.
- 139 K. Niu, Y. Zhang, J. Chen and X. Lu, *ACS Sens.*, 2022, **7**, 3551–3559.
- 140 Y. Tang, W. Li, Y. Muhammad, S. Jiang, M. Huang, H. Zhang, Z. Zhao and Z. Zhao, *Chem. Eng. J.*, 2021, **421**, 129743.
- 141 H. Zhao, G. Liu, Y. Liu, X. Liu, H. Wang, H. Chen, J. Gao and Y. Jiang, *ACS Appl. Mater. Interfaces*, 2022, **14**, 2881–2892.
- 142 Y. Zheng, S. Zhang, J. Guo, R. Shi, J. Yu, K. Li, N. Li, Z. Zhang and Y. Chen, *Angew. Chem., Int. Ed.*, 2022, **61**, e202208744.
- 143 S. Qiao, M. Li, J. Yu, S. Zhang, D. Yan, Z. Zhang and Y. Chen, *Particuology*, 2022, **64**, 140–144.

