Chemical Science



EDGE ARTICLE

View Article Online
View Journal | View Issue



Cite this: Chem. Sci., 2016, 7, 4930

Stabilizing metastable tetragonal HfO₂ using a non-hydrolytic solution-phase route: ligand exchange as a means of controlling particle size†

Gregory R. Waetzig,^a Sean W. Depner,^b Hasti Asayesh-Ardakani,^{cd} Nicholas D. Cultrara,^b Reza Shahbazian-Yassar^{cde} and Sarbajit Banerjee*^a

There has been intense interest in stabilizing the tetragonal phase of HfO_2 since it is predicted to outperform the thermodynamically stable lower-symmetry monoclinic phase for almost every application where HfO_2 has found use by dint of its higher dielectric constant, bandgap, and hardness. However, the monoclinic phase is much more thermodynamically stable and the tetragonal phase of HfO_2 is generally accessible only at temperatures above 1720 °C. Classical models comparing the competing influences of bulk free energy and specific surface energy predict that the tetragonal phase of HfO_2 ought to be stable at ultrasmall dimensions below 4 nm; however, these size regimes have been difficult to access in the absence of synthetic methods that yield well-defined and monodisperse nanocrystals with precise control over size. In this work, we have developed a modified non-hydrolytic condensation method to precisely control the size of HfO_2 nanocrystals with low concentrations of dopants by suppressing the kinetics of particle growth by cross-condensation with less-reactive precursors. This synthetic method enables us to stabilize tetragonal HfO_2 while evaluating ideas for critical size at which surface energy considerations surpass the bulk free energy stabilization. The phase assignment has been verified by atomic resolution high angle annular dark field images acquired for individual nanocrystals.

Received 11th April 2016 Accepted 3rd May 2016

DOI: 10.1039/c6sc01601d

www.rsc.org/chemicalscience

Introduction

A particularly powerful aspect of nanoscience that enables much new functionality derives from the greatly altered phase equilibria obtained upon confining materials to nanoscale dimensions.¹⁻⁴ The increased contributions from surface free energy terms can outweigh bulk free energy considerations and enable the stabilization of crystalline phases under ambient conditions that can otherwise only be stabilized at high temperatures and pressures. As a few notable examples of such metastable phases and their interesting properties: a metallic 1T phase is stabilized upon exfoliating the bulk semiconducting 2H-phases of MoS₂ and WS₂ to few-layered sheets^{5,6} and shows

structure that is otherwise stable only above ca. 1720 °C.16

greatly improved activity as a catalyst for hydrogen evolution;

a γ-MoC phase is stabilized in preference to β-Mo₂C for nano-

structures of molybdenum carbide and also exhibits promising reactivity for hydrogen evolution;7 the tetragonal phase of ZrO2 is stabilized in preference to the monoclinic phase for particles below a critical size of ca. 30 nm and is used for the transformation toughening of ceramics;8,9 and a metastable LixFePO4 phase is stabilized upon electrochemically delithiating LiFePO₄ nanoparticles at high rates within a Li-ion battery and mitigates the need to go through a much slower nucleation and growth process that would result in phase segregation of LiFePO4 and FePO₄.10,11 Stabilizing metastable structures requires careful control of particle size and the kinetics of crystallization processes. Low-temperature solution-phase routes for defining structural frameworks are particularly well-suited for preparing kinetically trapped metastable structures since the energetics of these reactions are often too low to allow for coarsening of grain size or overcoming shallow valleys in the potential energy landscape. 12-15 In this work, we demonstrate a cross-coupling ligand exchange method for controlling the particle size in the non-hydrolytic sol-gel condensation growth of HfO2 nanocrystals. Precise control of the size of HfO2 nanocrystals enables unequivocal determination of the critical size required to stabilize the tetragonal phase and provides access to welldefined crystals of this technologically important metastable

[&]quot;Department of Chemistry and Department of Materials Science and Engineering, Texas A&M University, College Station, TX 77845-3012, USA. E-mail: banerjee@ chem.tamu.edu

^bDepartment of Chemistry, University at Buffalo, The State University of New York, Buffalo, New York 14260-3000, USA

Department of Mechanical Engineering-Engineering Mechanics, Michigan Technological University, Houghton, Michigan 49933-1295, USA

^aDepartment of Physics, University of Illinois at Chicago, Chicago, Illinois 60607-7059, USA

^{*}Department of Mechanical and Industrial Engineering, University of Illinois at Chicago, Chicago, Illinois 60607-7059, USA

[†] Electronic supplementary information (ESI) available. See DOI: 10.1039/c6sc01601d

Edge Article Chemical Science

Tetragonal ZrO2 has been widely accessible for several decades, even without incorporation of dopant atoms, since the critical size at which the surface free energy terms overcome bulk free energy considerations is relatively large, variously estimated to be ca. 15-30 nm.8,9,17-19 In contrast, stabilization of the tetragonal phase of HfO2 is much more challenging since: (a) the bulk free energy stabilization of the monoclinic phase over the tetragonal phase is almost 40% greater for HfO₂ as compared to ZrO2; and (b) the volume expansion accompanying the tetragonal to monoclinic phase transition is much smaller for HfO₂ (ca. 2.7%) as compared to ZrO₂ (4.0%).^{20,21} Estimates of the critical size required to stabilize the tetragonal phase of HfO₂ vary widely from about 2 to 10 nm but it is clear that this value is substantially smaller than the critical size for ZrO2.16,20,22 Several methods for the preparation of nanometer-sized particles of HfO2 report the stabilization of at least some fraction of tetragonal HfO2; for instance, signatures of the tetragonal phase have been identified in particles obtained by the thermal decomposition of pure Hf(OH)4,16 the oxidation of metallic Hf nanocrystals,23 and a ligand-mediated reaction at the interface of water and oil phases.24 However, the polydispersity and relatively poor crystallinity of the particles obtained by these methods implies that the obtained samples almost always contain only minor proportions of tetragonal phases and a clear delineation of a size-dependent phase diagram has thus far not been possible. Several instances of stabilizing tetragonal domains have also been reported for thin films of HfO₂ prepared by methods such as atomic layer deposition in a lowoxygen environment,25 ultra-thin films deposited onto clean Si (100) surfaces by atomic layer deposition,26 and ion-beamassisted deposition in an oxygen deficient ambient.27 Again, the films usually contain mixtures of multiple crystalline and amorphous phases and exhibit considerable heterogeneity in terms of the dimensions of individual domains.

The stabilization of tetragonal HfO₂ is not just an academic curiosity. Indeed, the tetragonal (space group P42/nmc) phase of HfO₂ is anticipated to outperform the thermodynamically stable lower-symmetry monoclinic phase (space group $P2_1/c$) for almost every application where HfO2 has found use. Perhaps the most important application of HfO2 is in gate dielectric stacks as a high-κ dielectric because of its resistance to silicidation and silicate formation and its much greater dielectric constant as compared to SiO2. 20,28-30 First-principles calculations predict a dielectric constant of 18 for monoclinic HfO2, which is far surpassed by the value of almost 70 predicted for tetragonal HfO2.31 The bandgap of the tetragonal phase is also predicted to be larger (ca. 6.11 eV) as compared to the monoclinic phase (5.78 eV).32 Finally, the tetragonal phase is denser and has been experimentally found to have a higher Knoop hardness.27

In comparison to aqueous methods, non-hydrolytic methods, often based on formation of oxo-bridges by elimination of small molecules, provide considerable control of the kinetics of condensation.14,15,33 Such control is imperative to precisely control particle size and morphology when growing nanoparticles. In an early work, the condensation of hafnium alkoxides in benzyl alcohol with the elimination of alkyl ethers yielded monoclinic, but not tetragonal, HfO2 nanocrystals.34

Solvothermal processing of various hafnium alkoxides yielded varying morphologies of HfO2 nanocrystals, again crystallized in the monoclinic phase.35 Hyeon and co-workers adapted the alkyl halide elimination route first proposed by Vioux for the growth of nanocrystals and were able to achieve the multigram synthesis of ZrO2 nanocrystals as per:17,36

$$\equiv M-X + \equiv M-O-R \rightarrow \equiv M-O-M \equiv + R-X$$
 (1)

Brus and co-workers extended this method to prepare HfO₂ and solid-solution Hf_xZr_{1-x}O₂ nanocrystals and established considerable control over the relative Hf: Zr concentrations.19 In previous work, we have demonstrated that the R group of the alkoxide ligand allows for substantial tunability of the size of HfO₂ and ZrO₂ nanocrystals as well as the relative Hf: Zr ratios of Hf_xZr_{1-x}O₂ nanocrystals.^{37,38} These studies as well as past work by Vioux have established that upon reacting M(OR)₄ and MX4 species, substantial ligand exchange takes place to stabilize haloalkoxides such as M(OR)₃Cl, M(OR)₂Cl₂, and M(OR) Cl₃.14,36 The first of these three species has been proposed as a catalyst that brings about transformation of an alkoxo-bridge to an oxo-bridge as per the reaction depicted in Scheme 1.

When two different metal precursors are reacted, the composition of the product depends on the relative condensation rates and reactivities. For metals exhibiting comparable reactivity, such as Hf and Zr, the heterocondensation reaction yields solid-solution nanocrystals and can be written as follows:18,19

$$mMX_n + nM'(OR)_m \rightarrow M_mM'_nO_{nm} + nmRX$$
 (2)

However, if the rates of homo- and hetero-condensation are vastly different, the products of the faster reaction are obtained preferentially. In this work, we find that adding a much less reactive precursor, either $Ce(O^tBu)_4$ or $La(O^iPr)_3$, greatly modifies the concentration of the active monomer depicted in Scheme 1 and thereby retards the kinetics of the homocondensation reaction, yielding considerable control over the

Scheme 1 Non-hydrolytic condensation of metal halide and metal alkoxide to form an alkoxo-bridge intermediate. A "catalyst", MX3OR, initiates conversion of the alkoxo-bridge to an oxo-bridge then subsequently eliminates an alkyl halide to form the desired metal oxide-product

Chemical Science

size of HfO2 nanocrystals with only minimal incorporation of La and Ce. This unprecedented control of nanocrystal size allows us to explore ultra-small dimensions and determine the critical size for stabilizing the tetragonal phase of HfO₂.

Experimental

Synthesis

Hafnium(w) chloride, cerium(m) chloride, lanthanum(m) chloride, lanthanum(III) iso-propoxide, and tri-n-octylphosphine oxide (TOPO) were purchased from Strem and used without any further purification. Hafnium(IV) tert-butoxide was purchased from Alfa Aesar and used as received. Cerium(iv) tert-butoxide was purchased from Gelest and used without further purification. To synthesize the metal oxide nanocrystals, a metal halide and metal alkoxide are mixed in equimolar amounts with ca. 10 g of TOPO in a three-neck round bottom flask under an Ar ambient within a glovebox. The total concentration of metal precursors is maintained at 4 mmol in all of the reactions. In all of the reactions, 2 mmol of HfCl4 is used as the chloride precursor, whereas the alkoxide precursor is x mmol of $La(O^{i}Pr)_{3}$ or $Ce(O^{t}Bu)_{4}$ and 4 - x mmol of $Hf(O^{t}Bu)_{4}$. CeO_{2} nanocrystals were obtained by the reaction of equimolar amounts of CeCl₃ and Ce(O^tBu)₄ as reported in our previous work.39 Reducing the amount of the chloride precursor below equimolar amounts solely yields amorphous products as discussed in further detail below.

Briefly, the reaction mixture is heated under an argon ambient on a Schlenk line to ca. 60 °C, until the TOPO is melted at which point stirring is initiated. Subsequently, the reaction mixture is heated to 340 °C and kept at this temperature for 2 h. Next, the reaction mixture is cooled to ca. 60 °C and solvent/ non-solvent washing is performed alternating acetone and hexanes to remove excess TOPO.

Characterization

A Rigaku Ultima IV diffractometer with a graphite monochromator and a Bruker-AXS D8 Advanced Bragg-Brentano Xray powder diffractometer, both using Cu K α radiation (λ = 1.5418 Å), were used for characterization of the samples by powder X-ray diffraction. The crystallinity and size distribution of the nanocrystals was evaluated by high-resolution transmission electron microscopy (HRTEM) using JEOL-2010 and FEI Tecnai G2 F20 ST electron microscopes at an operating voltage of 200 kV. Samples for HRTEM analysis were dispersed in hexanes, drop-cast onto 400-mesh carbon-coated copper grids, and allowed to dry in air. The stoichiometry of the nanocrystals was determined by X-ray fluorescence (XRF) measurements, conducted by Oneida Research Services, Inc. in Whitesboro, NY, by inductively coupled plasma-mass spectrometry (ICP-MS) using a Perkin Elmer DRCII instrument, and by energy dispersive X-ray spectroscopy (EDX) on a JEOL JSM-7500F field emission scanning electron microscope (FE-SEM) operated at an accelerating voltage of 20 kV. Samples for ICP-MS analysis were prepared by acid digestion in an aqueous solution of 67% metals grade HNO3. Further characterization was

performed using atomic resolution high-angle annular darkfield (HAADF) imaging. A probe-corrected JEOL JEM-ARM200CF instrument equipped with a cold field-emission gun operated at 200 kV was used with a convergence angle of 22 mrad. The HAADF inner detector angle was 90 mrad.

Results

Fig. 1 displays XRD patterns for nanocrystals obtained by the reaction of HfCl₄ with varying proportions of Hf(O^tBu)₄ and $Ce(O^tBu)_4$. Table 1 lists the actual Hf and Ce atomic concentrations obtained for the different precursor ratios as well as the primary phase identified from analysis of powder XRD patterns. Energy dispersive X-ray spectroscopy (EDX) was also performed on the Hf_{1-x}Ce_xO₂ nanocrystals and provides good agreement with the hafnium and cerium concentrations derived by elemental analysis (Fig. S1 and Table S1, ESI†). Decreasing the concentration of HfCl₄ below 2 mmol results in the formation of entirely amorphous aggregates and thus Hf: Ce concentrations with excess cerium in the reaction mixture are not further discussed. Lower alkoxide concentrations further yield amorphous products. HfO2 nanocrystals prepared by the reaction of $Hf(O^tBu)_4$ and $HfCl_4$ are clearly monoclinic $(P2_1/c)$ as delineated by the appearance of sharp (200) and (220) reflections (Joint Committee on Powder Diffraction Standards (JCPDS) 78-0050) indexed in Fig. 1A.37,38 In contrast, CeO2 nanocrystals crystallize in a cubic fluorite structure $(Fm\bar{3}m)$ with reflections that can be indexed to JCPDS# 34-0394 (Fig. S2, ESI†). As the concentration

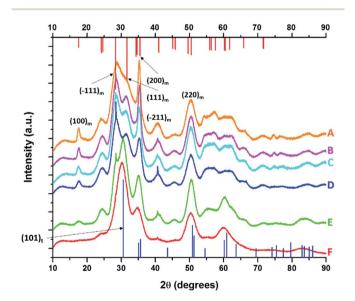


Fig. 1 X-ray diffraction patterns of end-member pure HfO2 (A) compared to $Hf_{1-x}Ce_xO_2$ nanocrystals prepared by the reaction of HfCl₄ with varying proportions of Hf(O^tBu)₄ and Ce(O^tBu)₄. The patterns correspond to detected (and precursor) relative Hf concentrations. The precursors are listed in Table 1. (A) 100% (100%), (B) 99.87% (90%), (C) 99.87% (80%), (D) 99.68% (70%), (E) 99.36% (60%) and (F) 97.64% (50%). Vertical bars indicate positions and relative intensities of reflections expected from JCPDS patterns. Reflections of monoclinic HfO2 are indicated in red (JCPDS # 78-0050) and tetragonal HfO2 in blue (XRD pattern simulated as described in the text)

Table 1 Relative amounts of precursors used in the synthesis of HfO_2 nanocrystals, the atomic percentage of Hf as a function of the total metal content, the detected relative Hf and Ce concentrations, the length of the nanorods determined from statistical analysis of TEM data (the width is invariant at ca. 2.5 nm), and the predominant phase determined by powder X-ray diffraction

HfCl ₄ [mmols]	$Hf(O^{-t}But)_4$ [mmols]	Ce(O- ^t But) ₄ [mmols]	Precursor Hf concentration [relative at%]	Detected Hf concentration [relative at%]	Detected Ce concentration [relative at%]	Length of nanocrystals [nm]	Phase of nanocrystals
2.0	2.0	0.0	100	100.0	0	12.9 ± 1.8	Monoclinic
2.0	1.6	0.4	90	99.87	0.13	9.5 ± 2.2	Monoclinic
2.0	1.2	0.8	80	99.87	0.13	7.8 ± 1.9	Monoclinic
2.0	0.8	1.2	70	99.68	0.32	5.9 ± 1.0	Monoclinic
2.0	0.4	1.6	60	99.36	0.64	4.4 ± 0.7	Monoclinic/tetragonal
2.0	0	2	50	97.64	2.36	3.1 ± 0.4	Tetragonal
0.0	0.0	4.0	0	0	100	1.5 ± 0.5	Cubic

of Hf is decreased, or in other words, the relative ratio of $Ce(O^tBu)_A$ to $Hf(O^tBu)_A$ is increased, the reflections are broadened indicating a pronounced diminution in size even though elemental analysis data presented in Table 1 suggests very little Ce incorporation. In contrast to the rest of the series, reaction between 2 mmol of HfCl₄ and 2 mmol of Ce(O^tBu)₄ preponderantly yields the tetragonal phase of HfO₂ characterized by a pronounced (101) reflection centered at $2\theta = 30.3^{\circ}$ (Fig. 1F). The simulated pattern of tetragonal HfO2 has been generated using coordinates for a relaxed structure of this phase calculated by Perevalov and co-workers and is depicted in blue in Fig. 1 (a complete structure solution is thus far absent for this phase).40 Table S2 in the ESI† lists the atomic coordinates, lattice constants, and angles of the monoclinic and tetragonal phases of HfO2 with the latter set of data being derived from the calculation noted above. Careful examination of Fig. 1E, the XRD pattern for the sample prepared with 1.6 mmol of $Ce(O^tBu)_4$, indicates the appearance of a reflection at $2\theta = 31^\circ$ that can be attributed to the (101) reflection of the tetragonal phase and suggests that this set of precursors yields a mixture of tetragonal and monoclinic phases. A reflection at $2\theta = ca$. 41° in Fig. 1E suggests trace amounts of the monoclinic phase although the tetragonal phase is clearly vastly preponderant.

Fig. 2 indicates HRTEM images and size distribution histograms for these nanocrystals. Table 1 lists the dimensions determined by statistical analysis of at least 50 nanocrystals. With increasing concentration of $Ce(O^tBu)_4$ in the reaction mixture, the morphology of the obtained nanostructures evolves from elongated nanorods to quasi-spherical particles. The nanorods preferentially grow along the [100] direction of monoclinic HfO2.38 As also suggested by the powder XRD data of Fig. 1, the lengths of the $Hf_{1-x}Ce_xO_2$ nanorods are monotonically diminished with reduced concentration of Hf(O^tBu)₄ with respect to $Ce(O^tBu)_4$. The average length is decreased from 12.9 \pm 1.8 nm for monoclinic nanocrystals grown using only $Hf(O^tBu)_4$ to 3.1 \pm 0.4 nm for tetragonal nanocrystals grown using Ce(O^tBu)₄ as the only alkoxide precursor. The widths of the $Hf_{1-x}Ce_xO_2$ nanocrystals are not substantially altered and remain around 2.5 \pm 0.4 nm. The lattice-resolved HRTEM image in Fig. 2F clearly indicates a lattice separation of 0.292 nm corresponding to the predicted separation between the

(101) planes of tetragonal HfO₂ (Table S2†),⁴⁰ corroborating the stabilization of this metastable phase under these conditions.

To verify the phase assignment of $Hf_{1-x}Ce_xO_2$ as being tetragonal, atomic-resolution HAADF scanning transmission electron microscopy (STEM) imaging has been performed using an aberration corrected microscope. Fig. 3 indicates HAADF STEM images and fast Fourier transforms (FFT) acquired for two different nanocrystals along the [010] and [111] zone axes. The simulated diffraction patterns for these zone axis assignments using coordinates of the tetragonal structure are an excellent match to the experimental data (as indicated by the reconstructed solid spheres depiction), providing unequivocal corroboration of the tetragonal crystal structure. Fig. S3A and B† indicate the planes of atoms in the tetragonal unit cell that are indexed in the simulated diffraction patterns (Fig. 3D and H) for each image acquired along a specific zone axis.

Fig. 4 displays powder XRD patterns acquired for nanocrystals obtained by the reaction of HfCl4 with varying proportions of Hf(O^tBu)₄ and La(OⁱPr)₃. Table 2 lists the actual Hf and La atomic concentrations obtained for the different precursor ratios as well as the primary phase identified from analysis of powder XRD patterns. EDX was also performed on Hf_{1-r}La_rO₂ nanocrystals and the determined hafnium and lanthanum concentrations are in good agreement with the elemental analysis results (Fig. S4 and Table S3†). Again, upon decreasing the Hf: La ratios such that there is a lower concentration of hafnium precursors as compared to lanthanum precursors, only amorphous aggregates are obtained, and thus we focus our discussion on reaction mixtures with lower concentrations of La(O¹Pr)₃ as listed in Table 2. Lower alkoxide concentrations also yield amorphous aggregates. Notably, the homocondensation of LaCl₃ and La(O'Pr)3 yields LaOCl nanocrystals crystallized in the matlockite PbFCl-type phase.41-43

Analogous to the above discussion for Ce(O^tBu)₄, with increasing concentration of La(OⁱPr)₃ in the reaction mixture, the (100) and (200) reflections indexed to the monoclinic phase of pure HfO₂ are broadened and diminished in intensity suggesting a pronounced diminution in size. Again, although the powder XRD patterns are substantially altered, the elemental analysis results listed in Table 2 indicate very little incorporation of La in HfO₂. For the sample prepared by the reaction of

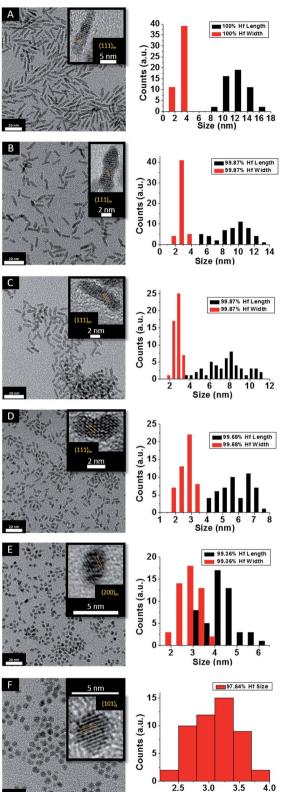


Fig. 2 Low-magnification transmission electron microscopy images of HfO_2 (A) nanocrystals compared to nanocrystals prepared by the reaction of $HfCl_4$ with varying proportions of $Hf(O^tBu)_4$ and $Ce(O^tBu)_4$. The precursors and calculated dimensions are listed in Table 1. The detected (and precursor) relative Hf concentrations of (A) 100% (100%), (B) 99.87% (90%), (C) 99.87% (80%), (D) 99.68% (70%), (E) 99.36% (60%), and (F) 97.64% (50%). Insets show HRTEM images. The lattice-resolved

 $\rm HfCl_4$ and $\rm La(O^iPr)_3$, the (100) monoclinic reflection is no longer observed and the (101) tetragonal reflection becomes the most prominent feature in the powder XRD pattern suggesting stabilization of the tetragonal phase of $\rm HfO_2$ with modest La doping.

HRTEM images and size distribution histograms of this set of nanocrystals are shown in Fig. 5 and the relevant dimensions and standard deviations deduced from statistical analysis are listed in Table 2. With increasing concentration of La(OⁱPr)₃, the Hf_{1-x}La_xO₂ nanocrystals again evolve from elongated nanorods to quasi-spherical nanocrystals. The width of the Hf_{1-x}La_xO₂ nanocrystals is relatively unchanged at *ca.* 2.5 \pm 0.4 nm for the entire set of samples. However, the length of the nanorods is diminished from 12.9 \pm 1.8 nm for monoclinic nanocrystals grown using only Hf(O^fBu)₄ to 3.3 \pm 0.4 nm for Hf_{1-x}La_xO₂ tetragonal nanocrystals grown using La(OⁱPr)₃ as the only alkoxide precursor.

To confirm the phase assignment of $\mathrm{Hf}_{1-x}\mathrm{La}_x\mathrm{O}_2$ nanocrystals as being tetragonal, atomic-resolution HAADF STEM images and fast Fourier transforms (FFT) of the HAADF images were acquired and are depicted in Fig. 6. Images were acquired for different nanocrystals along [100] and [110] zone axes. The simulated diffraction patterns are an excellent match to the Fourier transforms in each case and the reconstructed tetragonal lattice (depicted as solid spheres) is entirely superimposable on the STEM image. Fig. S5A and B† indicate the planes of atoms in the tetragonal unit cell that are indexed in the simulated diffraction patterns (Fig. 6D and H). The STEM data further provides unambiguous confirmation of the tetragonal crystal structure.

The preceding discussion illustrates that the addition of $Ce(O^tBu)_4$ and $La(O^iPr)_3$ leads to a substantial and monotonic diminution of nanocrystal size even though elemental analysis results indicate that relatively low concentrations of Ce and La are actually incorporated within the lattice. At the smallest dimensions, the tetragonal phase of HfO_2 is stabilized over the monoclinic phase. These results lead to two fundamental questions regarding the mechanistic basis for the size control achieved by addition of La and Ce precursors and the origin of the altered phase stability.

Discussion

To understand the origin of the size control achieved by the addition of $Ce(O^tBu)_4$ and $La(O^iPr)_3$, it is important to consider the overall equation depicted in eqn (1), which results in formation of an oxo-bridge with the elimination of an alkyl halide, as well as the catalytic scheme proposed by Vioux shown in Scheme 1.^{44,45} Indeed, it is thought that the initial step in

images indicate separations between the (111) and (200) lattice planes of the monoclinic phase in the insets to (A) to (E). The separation between the (101) lattice planes of the tetragonal phase is indicated in the inset to (F). The accompanying size distribution histograms are shown to the right of each sample illustrating that the length of the nanorods decreases with increasing concentration of $Ce(O^tBu)_4$ in the synthesis, whereas the width remains relatively constant.

Edge Article

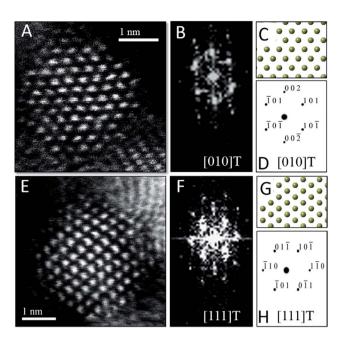


Fig. 3 Scanning transmission electron microscopy analysis of Hf_{1-x} - Ce_xO_2 tetragonal nanocrystals. (A) Atomic-resolution HAADF image and (B) FFT of (A) acquired along the [010] zone axis of the tetragonal structure. (C) Solid sphere model of the tetragonal structure corresponding to the [010] zone axis and (D) simulated diffraction pattern based on (C), both confirming the tetragonal crystal structure of (A). (E) Atomic-resolution HAADF image and (F) FFT of (E) acquired along the [111] zone axis of the tetragonal structure of another nanocrystal. (G) Solid sphere model of the tetragonal structure corresponding to the [111] zone axis and (H) simulated diffraction pattern based on (G).

a heterocondensation reaction between two metal precursors M and M' involves ligand exchange and can be written as:

$$MCl_n + M'(OR)_n \rightarrow MCl_{n-x}(OR)_x + M'Cl_x(OR)_{n-x},$$
 (3)

Evidence for such ligand-exchange comes from direct observations of chloroalkoxides by Vioux14,36 as well as the following observations derived from nanocrystal synthesis: (a) reactions of HfCl4 and Zr(OR)4 and ZrCl4 and Hf(OR)4 yield exactly the same compositions of solid-solution Hf_xZr_{1-x}O₂ nanocrystals suggesting that ligand scrambling precedes condensation;37 (b) the reaction of trivalent lanthanide chlorides and lanthanide alkoxides vields lanthanide oxyhalide nanocrystals with well-defined oxyhalide bridges.41-43 The rates of condensation of the chloroalkoxide species produced as per eqn (3) are greatly dependent on the specific metal; precursors with similar reactivities yield solid-solution nanocrystals with a random distribution of two metals, whereas if one species reacts much faster than the second, very little of the second species incorporates within the lattice and the oxide of the first metal is obtained as the primary product.³⁶ Reasonably wellmatched precursor pairs such as Hf/Zr and La/Ce yield solidsolution nanocrystals of Hf_rZr_{1-r}O₂ and La_rCe_{1-r}O₂, respectively, albeit with compositions that reflect the relative reactivities of the two metal precursors as modified by the alkoxide ligands. 18,37,39 However, upon reacting Hf precursors with Ce and La precursors, the homocondensation of the former

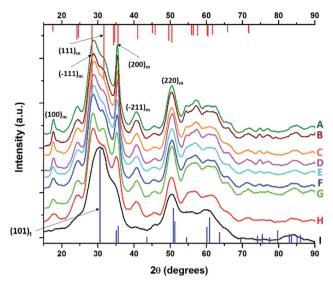


Fig. 4 X-ray diffraction patterns of pure HfO_2 (A) compared to $Hf_{1-x}La_xO_2$ nanocrystals prepared by the reaction of $HfCl_4$ with varying proportions of $Hf(O^tBu)_4$ and $La(O^iPr)_3$. The patterns correspond to detected (and precursor) relative Hf concentrations. The precursors are listed in Table 2. (A) 100% (100%), (B) 99.98% (97.5%), (C) 99.78% (93.75%), (D) 99.56% (87.5%), (E) 98.87% (75%), (F) 98.68% (62.5%), (G) 98.07% (56.25%), (H) 96.46% (52.5%), and (I) 95.27% (50%). Vertical bars indicate positions and relative intensities of reflections expected from JCPDS patterns. Reflections of monoclinic HfO_2 are indicated in red (JCPDS # 78-0050) and tetragonal HfO_2 in blue (XRD pattern simulated as described in the text).

proceeds much faster than heterocondensation. Indeed, HfO₂ with very low dopant concentrations is obtained as the exclusive product upon the reaction of HfCl₄ with mixtures of Hf(O^tBu)₄ and $Ce(O^tBu)_4/La(O^iPr)_3$. The relatively low incorporation of Ce and La within the doped HfO2 lattice, very much lower than the precursor concentrations, corroborates the idea of the lower reactivity of these precursors. Fig. 1, 2, 4, and 5 nevertheless indicate that the addition of Ce(O^tBu)₄ and La(OⁱPr)₃ allows for substantial tunability of the size of the obtained doped HfO₂ nanocrystals. In Scheme 1, the initial step involves the formation of an alkoxo-bridge as a result of a Lewis acid-Lewis base interaction between the oxygen atom of the alkoxide and the metal center of a halide. Subsequently, the MX₃OR species (derived from ligand exchange as per eqn (3)) mediates conversion of the alkoxo-bridge to an oxo-bridge with elimination of an alkyl halide. Indeed, Vioux has shown that the presence of MX₃OR species is imperative for condensation and that MX₂(OR)₂ and MX(OR)₃ species are much less reactive.³⁶ In other words, the Lewis acid-base complex depicted in Scheme 1 is the "monomer", whereas the MX₃OR species formed by ligand exchange serves as the catalyst. The retention of equimolar amounts of halide and alkoxide precursors ensures that the amount of catalyst is kept essentially the same for all of the reactions listed in Tables 1 and 2 as a result of the ligand exchange reaction depicted in eqn (3) although it must be qualified that the equilibrium constants for formation of the catalyst will be altered for the different alkoxides. Indeed, since formation of an oxo-bridge, and not diffusion of monomers, is

This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.

Open Access Article. Published on 03 May 2016. Downloaded on 12/5/2025 3:20:20 PM.

Table 2 Relative amounts of precursors used in the synthesis of HfO₂ nanocrystals, the atomic percentage of Hf as a function of the total metal content, the detected relative Hf and La concentrations, the length of the nanorods determined from statistical analysis of TEM data (the width is invariant at ca. 2.5 nm), and the predominant phase determined by powder X-ray diffraction

HfCl ₄ [mmols]	$Hf(O^{-t}But)_4$ [mmols]	La(O- ⁱ Pro) ₃ [mmols]	Precursor Hf concentration [relative at%]	Detected concentration [relative at%]	Detected Ce concentration [relative at%]	Length of nanocrystals [nm]	Phase of nanocrystals
2.0	2.00	0.00	100	100.0	0.00	12.9 ± 1.8	Monoclinic
2.0	1.90	0.10	97.50	99.98	0.01	11.5 ± 1.26	Monoclinic
2.0	1.75	0.25	93.75	99.78	0.22	10.1 ± 0.89	Monoclinic
2.0	1.50	0.50	87.50	99.56	0.44	9.3 ± 1.46	Monoclinic
2.0	1.00	1.00	75.0	98.87	1.13	8.1 ± 0.98	Monoclinic
2.0	0.50	1.50	62.50	98.68	1.32	7.0 ± 1.02	Monoclinic
2.0	0.25	1.75	56.25	98.07	1.93	5.9 ± 0.92	Monoclinic
2.0	0.10	1.90	52.50	96.46	3.54	4.7 ± 0.79	Monoclinic
2.0	0.00	2.00	50.00	95.27	4.73	3.3 ± 0.42	Tetragonal

thought to be the rate-determining step, in the absence of a sufficient amount of the catalyst, such as at low alkoxide concentrations, only amorphous aggregates are obtained. However, since the Lewis acid-base adducts constituted from HfCl₄ and Ce(O^tBu)₄/La(OⁱPr)₃ are much less reactive as compared to those prepared from HfCl₄ and Hf(O^tBu)₄, the addition of cerium and lanthanum precursors essentially reduces the concentration of the active monomer. In other words, the reaction rate is diminished as a result of the lower reactivity of mixed metal Lewis acid-base adducts towards formation of oxo-bridges. As further corroboration for this idea, Table 1 and Fig. 1 indicate that the homocondensation of hafnium precursors yields pure HfO2 nanocrystals that are 12.9 \pm 1.8 nm. In contrast, the homocondensation of cerium precursors yields CeO_2 nanocrystals that are 1.5 \pm 0.5 nm indicating much slower kinetics of growth (Table 1 and Fig. S2†). Cross-reactions between La and Ce alkoxides indicate even lower reactivities for the La precursors with only ca. 20 at% incorporation of La within solid-solution La_xCe_{1-x}O₂ nanocrystals when starting with equimolar concentrations.39 The reduced concentration of the active monomer brings about a systematic and pronounced diminution in the size of the doped HfO₂ nanocrystals by inhibiting their growth. In other words, the cross-condensation reaction enables modulation of the concentration of the active monomer, thereby enabling precise control over crystal size.

As a next point, we discuss the origins of the stabilization of the tetragonal phase of HfO₂. Indeed, the product of the direct reaction of HfCl₄ and Hf(O¹Pr)₄ when ramped at a rate of 15 °C to 500 °C during thermal analysis is monoclinic HfO2, the thermodynamically stable phase, along with an oxygen-deficient orthorhombic HfO2 phase. The inclusion of TOPO still yields monoclinic HfO2, albeit with a smaller size. These results illustrate that direct reaction of the precursors cannot yield the metastable, kinetically trapped phase. The incorporation of the La and Ce alkoxides is imperative to slow the kinetics of crystal growth. Fig. 7 indicates the evolution of size as a function of the measured Hf concentration in the doped nanocrystals and depicts that only below a critical threshold of ca. 3.6-3.8 nm is

the tetragonal phase stabilized. Since Tables 1 and 2 indicate that some amount of La and Ce are incorporated within the doped nanocrystals, it is worth considering whether the stabilization of the tetragonal phase results from (a) the size of the La/Ce cations that are displacively doped being different from that of Hf-cations (a strain effect), (b) the creation of oxygen vacancies, or (c) crystal size. Based on the larger size of La³⁺ cations (110 pm for seven-coordinated and 116 pm for eightcoordinated sites) as compared to Ce3+ (107 pm for sevencoordinated and 114.3 pm for eight-coordinated) or Ce⁴⁺ (97 pm for eight-coordinated),46,47 if the effects of cation size were to be of paramount importance, one would expect that incorporation of La would more readily bring about stabilization of the tetragonal phase and one would further expect to see substantial tensile strain. However, Tables 1 and 2 indicate that the amount of detected Ce and La are 2.36 at% and 4.73 at%, respectively, for stabilization of the tetragonal phase and thus size of the cations is likely not the primary driving force for stabilization of the tetragonal phase. Furthermore, the reconstructed HAADF images (Fig. 3 and 6) do not reveal any measurable strain for the tetragonal structure. In other words, if size were the primary factor, relatively lower amounts of Laincorporation would be expected to bring about stabilization of the tetragonal phase (Table 2 indicates that the $Hf_{1-x}La_xO_2$ nanocrystals remain monoclinic even upon incorporation of 3.54 at% of La).

The second scenario pertains to the potential role of oxygen vacancies. The substitutional incorporation of trivalent lanthanum cations in the HfO₂ lattice will result in creation of half an oxygen vacancy to maintain electrostatic neutrality. The Ce⁴⁺/Ce³⁺ redox couple is readily accessible but since we start with tetravalent cerium precursors, the vacancy concentration generated upon cerium-incorporation is likely to be lower than upon lanthanum incorporation. Again, if oxygen vacancies were to provide the driving force for stabilization of the tetragonal phase, one would expect that lanthanum-incorporation should more readily bring about stabilization of the tetragonal phase as compared to cerium incorporation. Again, Tables 1 and 2 indicate that Hf_{1-x}La_xO₂ nanocrystals with 3.54 at% La are

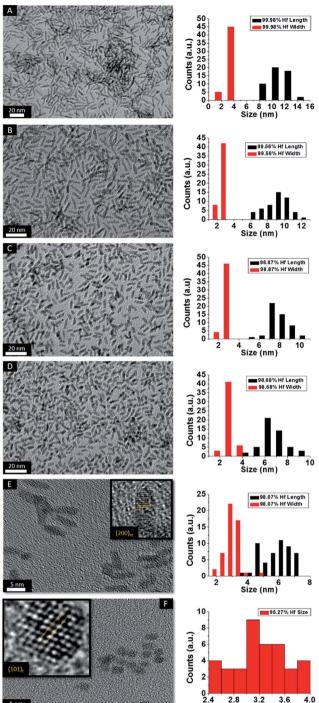


Fig. 5 Low-magnification transmission electron microscopy images of nanocrystals prepared by the reaction of HfCl $_4$ with varying proportions of Hf(O t Bu) $_4$ and La(O i Pr) $_3$. The precursors and calculated dimensions are listed in Table 2. The detected (and precursor) relative Hf concentrations of (A) 99.98% (97.5%), (B) 99.56% (87.5%), (C) 98.87% (75%), (D) 98.68% (62.5%), (E) 98.07% (56.25%), and (F) 95.27% (50%). Insets show HRTEM images. The lattice-resolved images indicate separations between the (200) lattice planes of the monoclinic phase in the inset of (E) and the (101) lattice planes of the tetragonal phase in the inset of (F). The accompanying size distribution histograms are shown to the right of each sample illustrating that the length of the nanorods decreases with increasing concentration of La(O i Pr) $_3$ in the synthesis, whereas the width remains relatively constant.

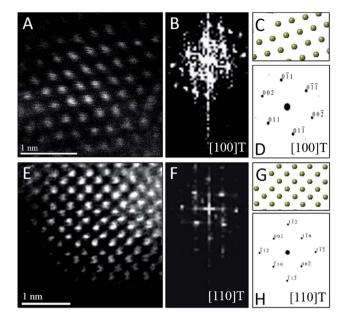


Fig. 6 Scanning transmission electron microscopy analysis of individual $Hf_{1-x}La_xO_2$ tetragonal nanocrystals. (A) Atomic-resolution HAADF image and (B) FFT of (A) acquired along the [100] zone axis of the tetragonal structure. (C) Solid sphere model of the tetragonal structure corresponding to the [100] zone axis and (D) simulated diffraction pattern based on (C), both confirming the crystal structure orientation of (A). (E) Atomic-resolution HAADF image and (F) FFT of (E) acquired along the [110] zone axis of the tetragonal structure of another nanocrystal. (G) Solid sphere model of the tetragonal structure corresponding to the [110] zone axis and (H) simulated diffraction pattern based on (G).

monoclinic, whereas $\mathrm{Hf_{1-x}Ce_xO_2}$ nanocrystals with only 2.36 at% Ce are tetragonal. The preceding discussion and Fig. 7 thus implies that it is the size of the nanocrystals that is the primary driving force for stabilization of the tetragonal phase. The stabilization of this phase is derived from the surface energy of the tetragonal phase being lower than that of the monoclinic phase (the difference between the two phases is 246 mJ m⁻²).²¹ Below the critical size regime, the surface-to-volume ratio of pure $\mathrm{HfO_2}$ nanocrystals becomes such that the surface energy term exceeds the bulk energy component of the free energy term (the difference between the two phases is 196 meV for pure $\mathrm{HfO_2}$),²¹ thereby enabling preferentially stabilization of the tetragonal phase at room temperature.^{1,2,8,9}

In 1972, Bailey and co-workers developed an expression for calculating the critical size for stabilizing a metastable state based on a classical thermodynamic treatment of the phase transformation and the competing bulk and surface energy terms. In this formulation, the critical size, d can be expressed as⁴⁸

$$d = \frac{6}{[(G_{\rm T} - G_{\rm M}) + (V_{\rm T} - V_{\rm M})]} \left(\frac{\gamma_{\rm M}}{\rho_{\rm M}} - \frac{\gamma_{\rm T}}{\rho_{\rm T}}\right) \tag{4}$$

where the subscripts M and T correspond to the relevant values for the monoclinic and tetragonal phases, G is the volume free energy change across the phase transformation, V is the strain energy, γ is the specific surface energy, and ρ represents the

| Monoclinic Regime | Critical Threshold | Critical Threshold | Hf at. %

Fig. 7 A plot of nanocrystal size versus the relative atomic percentage of Hf detected by elemental analysis (Tables 1 and 2). The line denoted as the critical threshold separates the monoclinic and tetragonal phases of pure HfO₂.

density. Hunter et al. used this expression to predict a critical size for stabilization of tetragonal HfO_2 of d=3.6 nm.¹⁶ In the absence of well-defined, monodisperse, and phase-pure nanocrystals, a comprehensive evaluation of this formalism has not been possible thus far. Another notable complication for HfO₂ nanocrystals prepared by aqueous methods is the almost 20-30% diminution of surface energy as a result of surface hydroxylation, which in this case further dilutes the influence of the surface energy contribution.²⁰ Fig. 7 indicates a critical size of 3.6–3.8 nm for stabilization of the tetragonal phase of HfO₂, which is in remarkably good agreement with predictions from this thermodynamic model. The origin of the stability of the tetragonal phase at these dimensions can thus be attributed to the substantially lower surface energies of this phase, which renders this phase energetically stable under conditions of constrained equilibrium.

Conclusions

Chemical Science

Stabilization of the tetragonal phase of HfO₂ has been far more challenging as compared to ZrO₂ given the smaller volume expansion accompanying the tetragonal → monoclinic transformation and the relatively greater stabilization enjoyed by the monoclinic phase. Classical thermodynamic models predict that the tetragonal phase should be stable at dimensions smaller than ca. 3.6 nm but the validity of these predictions have been thus far impossible to determine in the absence of synthetic approaches that can access such ultra-small dimensions with precise control of particle size. In this work, we have developed a non-hydrolytic condensation route wherein the concentration of the active monomer is precisely modulated by replacing $Hf(O^tBu)_4$ with less reactive $Ce(O^tBu)_4$ or $La(O^iPr)_3$ precursors. The latter alkoxides exhibit much slower kinetics of condensation and thus are incorporated within the doped HfO2 lattice only to small extents but play a significant role in modifying the growth kinetics by suppressing the concentration of the active monomer. This approach enables precise control of size in ultra-small dimensions and allows for systematic evaluation of the size-dependence of phase stabilities in this system. The much desired metastable tetragonal phase is stabilized at dimensions less than 3.6–3.8 nm, which is in good accord with predictions of thermodynamic models that take into account the competing influences of bulk free energy and specific surface energy.

Conflict of interest

The authors declare no competing financial interest.

Acknowledgements

The authors gratefully acknowledge support from the National Science Foundation under DMR 1504702. The authors would like to acknowledge that EDX analysis on the FE-SEM were performed at the Texas A&M University Materials Characterization Facility. The authors also want to acknowledge Dr Robert Dennis for help performing the EDX analysis of the nanopowders.

Notes and references

- 1 A. Navrotsky, ChemPhysChem, 2011, 12, 2207-2215.
- 2 T. Waitz, K. Tsuchiya, T. Antretter and F. D. Fischer, *MRS Bull.*, 2009, **34**, 814–821.
- 3 M. Grünwald, K. Lutker, A. P. Alivisatos, E. Rabani and P. L. Geissler, *Nano Lett.*, 2013, 13, 1367–1372.
- 4 S. H. Tolbert and A. P. Alivisatos, Science, 1994, 265, 373-376.
- 5 M. A. Lukowski, A. S. Daniel, F. Meng, A. Forticaux, L. Li and S. Jin, J. Am. Chem. Soc., 2013, 135, 10274–10277.
- 6 A. Ambrosi, Z. Sofer and M. Pumera, *Chem. Commun.*, 2015, 51, 8450–8453.
- 7 C. Wan, Y. N. Regmi and B. M. Leonard, *Angew. Chem., Int. Ed.*, 2014, 53, 6407–6410.
- 8 R. C. Garvie, J. Phys. Chem., 1965, 69, 1238-1243.
- 9 J. Chevalier, L. Gremillard, A. V. Virkar and D. R. Clarke, J. Am. Ceram. Soc., 2009, 92, 1901–1920.
- 10 H. Liu, F. C. Strobridge, O. J. Borkiewicz, K. M. Wiaderek, K. W. Chapman, P. J. Chupas and C. P. Grey, *Science*, 2014, 344, 1252817.
- 11 R. Malik, F. Zhou and G. Ceder, *Nat. Mater.*, 2011, **10**, 587–590.
- 12 J. Gopalakrishnan, Chem. Mater., 1995, 7, 1265-1275.
- 13 J. M. Hodges, K. Kletetschka, J. L. Fenton, C. G. Read and R. E. Schaak, *Angew. Chem., Int. Ed.*, 2015, 54, 8669–8672.
- 14 P. H. Mutin and A. Vioux, J. Mater. Chem. A, 2013, 1, 11504.
- 15 P. H. Mutin and A. Vioux, Chem. Mater., 2009, 21, 582-596.
- 16 O. Hunter Jr, R. W. Scheidecker and S. Tojo, Ceramurgia Int., 1979, 5, 137–142.
- 17 J. Joo, T. Yu, Y. W. Kim, H. M. Park, F. Wu, J. Z. Zhang and T. Hyeon, *J. Am. Chem. Soc.*, 2003, **125**, 6553–6557.
- 18 J. Tang, T. Zhang, P. Zoogman, J. Fabbri, S. W. Chan, Y. M. Zhu, L. E. Brus and M. L. Steigerwald, Adv. Funct. Mater., 2005, 15, 1595–1602.

19 J. Tang, J. Fabbri, R. D. Robinson, Y. Zhu, I. P. Herman,

M. L. Steigerwald and L. E. Brus, Chem. Mater., 2004, 16, 1336-1342.

Edge Article

- 20 W. Zhou, S. V. Ushakov, T. Wang, J. G. Ekerdt, A. A. Demkov and A. Navrotsky, J. Appl. Phys., 2010, 107, 1-7.
- 21 I. M. Iskandarova, A. A. Knizhnik, E. A. Rykova, A. A. Bagatur'yants, B. V. Potapkin and A. A. Korkin, Microelectron. Eng., 2003, 69, 587-593.
- 22 S. V. Ushakov, A. Navrotsky, Y. Yang, S. Stemmer, K. Kukli, M. Ritala, M. A. Leskelä, P. Fejes, A. Demkov, C. Wang, B.-Y. Nguyen, D. Triyoso and P. Tobin, Phys. Status Solidi B, 2004, 241, 2268-2278.
- 23 B. Matovic, J. Pantic, J. Lukovic, M. Cebela, S. Dmitrovic, M. Mirkovic and M. Prekajski, Ceram. Int., 2016, 42, 615-620.
- 24 J. Oi and X. Zhou, Colloids Surf., A, 2015, 487, 26-34.
- 25 D. Cho, H. S. Jung, I. Yu, J. H. Yoon, H. K. Kim, S. Y. Lee, H. Jeon, S. Han, J. H. Kim, T. J. Park, B. Park and C. S. Hwang, Chem. Mater., 2012, 24, 3534-3543.
- 26 I. MacLaren, T. Ras, M. MacKenzie, A. J. Craven, D. W. McComb and S. De Gendt, J. Electrochem. Soc., 2009, 156, 103.
- 27 R. R. Manory, T. Mori, I. Shimizu, S. Miyake and G. Kimmel, J. Vac. Sci. Technol., A, 2002, 20, 549.
- 28 G. D. Wilk, R. M. Wallace and J. M. Anthony, J. Appl. Phys., 2001, 89, 5243.
- 29 A. O'Hara, G. Bersuker and A. A. Demkov, J. Appl. Phys., 2014, 115, 183703.
- 30 X. Luo and A. A. Demkov, J. Appl. Phys., 2015, 118, 124105.
- 31 X. Zhao and D. Vanderbilt, Phys. Rev. B: Condens. Matter Mater. Phys., 2002, 65, 233106.
- 32 H. Jiang, R. I. Gomez-Abal, P. Rinke and M. Scheffler, Phys. Rev. B: Condens. Matter Mater. Phys., 2010, 81, 1-9.

- 33 R. Deshmukh and M. Niederberger, in The Sol-Gel Handbook-Synthesis, Characterization, and Applications, ed. D. Levy and M. Zayat, Wiley-VCH Verlag GmbH & Co. KGaA., 2015, pp. 29-49.
- 34 N. Pinna, G. Garnweitner, M. Antonietti M. Niederberger, Adv. Mater., 2004, 16, 2196-2200.
- 35 T. J. Boyle, L. A. M. Steele, P. D. Burton, S. M. Hoppe, C. Lockhart and M. A. Rodriguez, Inorg. Chem., 2012, 51, 12075-12092.
- 36 A. Vioux, Chem. Mater., 1997, 9, 2292-2299.
- 37 S. W. Depner, K. R. Kort and S. Banerjee, CrystEngComm, 2009, 11, 841.
- 38 S. W. Depner, N. D. Cultrara, K. E. Farley, Y. Oin and S. Banerjee, ACS Nano, 2014, 8, 4678-4688.
- 39 S. W. Depner, K. R. Kort, C. Jave, D. A. Fischer and S. Banerjee, J. Phys. Chem. C, 2009, 113, 14126-14134.
- 40 T. V. Perevalov, V. A. Gritsenko, S. B. Erenburg, A. M. Badalyan, H. Wong and C. W. Kim, J. Appl. Phys., 2007, 101, 053704.
- 41 K. R. Kort and S. Banerjee, *Inorg. Chem.*, 2011, **50**, 5539–5544.
- 42 K. R. Kort and S. Banerjee, Small, 2015, 11, 329-334.
- 43 G. R. Waetzig, G. A. Horrocks, J. W. Jude, L. Zuin and S. Banerjee, Nanoscale, 2016, 8, 979-986.
- 44 L. Bourget, R. J. P. Corriu, D. Leclercq, P. H. Mutin and A. Vioux, J. Non-Cryst. Solids, 1998, 242, 81-91.
- 45 P. Arnal, R. J. P. Corriu, D. Leclercq, P. H. Mutin and A. Vioux, Chem. Mater., 1997, 9, 694-698.
- 46 R. D. Shannon, Acta Crystallogr., 1976, 32, 751-767.
- 47 R. Dronskowski, in Computational Chemistry of Solid State Materials, Wiley-VCH Verlag GmbH & Co. KGaA, 2006, pp. 13-14.
- 48 J. E. Bailey, D. Lewis, Z. M. Librant and L. J. Porter, Trans. J. Br. Ceram. Soc., 1972, 71, 25-30.