

## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)Cite this: *Dalton Trans.*, 2017, **46**, 13994

# Solid state structures and properties of free-base 5,10,15-triphenylcorrole (TPCor) anions obtained by deprotonation and reduction. Effective magnetic coupling of spins in $(\text{Cp}^*\text{Cr}^+)(\text{H}^+)(\text{H}_2\text{TPCor}^{2-})\cdot\text{C}_6\text{H}_4\text{Cl}_2^\dagger$

Dmitri V. Konarev,<sup>a</sup> Dmitri R. Karimov,<sup>a</sup> Salavat S. Khasanov,<sup>b</sup> Alexander F. Shestakov,<sup>a</sup> Akihiro Otsuka,<sup>c,d</sup> Hideki Yamochi,<sup>c,d</sup> Hiroshi Kitagawa<sup>c</sup> and Rimma N. Lyubovskaya<sup>a</sup>

The reduction of 5,10,15-triphenylcorrole ( $\text{H}_3\text{TPCor}$ ) with decamethylchromocene yields  $(\text{Cp}^*\text{Cr}^+)(\text{H}^+)(\text{H}_2\text{TPCor}^{2-})\cdot\text{C}_6\text{H}_4\text{Cl}_2$  (**1**). It is accompanied by the deprotonation of  $\text{H}_3\text{TPCor}$  and the formation of planar  $\text{H}_2\text{TPCor}^{2-}$  radical dianions. Complex **1** manifests a band at about 750 nm observed in the solution spectra of  $\text{H}_2\text{TArlylCor}^{2-}$  and demonstrates an EPR signal attributed to the reduced corrole macrocycle. The magnetic moment of **1** of  $4.10\mu_{\text{B}}$  at 300 K indicates the contribution of  $\text{Cp}^*\text{Cr}^+$  ( $S = 3/2$ ) and  $\text{H}_2\text{TPCor}^{2-}$  ( $S = 1/2$ ). These paramagnetic species alternate in the  $\pi$ -stacks providing rather effective antiferromagnetic coupling of spins at the Weiss temperature of  $-31$  K. To distinguish the  $\text{H}_2\text{TPC}^{2-}$  dianions from the deprotonated  $\text{H}_2\text{TPCor}^-$  anions, we also studied the {cryptand[2,2,2]( $\text{Na}^+$ )}( $\text{H}_2\text{TPCor}^-$ ) $\cdot 0.5\text{C}_6\text{H}_4\text{Cl}_2$  (**2**) salt with deprotonated corrole anions. In this case, a planar macrocycle was formed as well. However, the properties of  $\text{H}_2\text{TPCor}^-$  in **2** differ from those of  $\text{H}_2\text{TPCor}^{2-}$  in **1**.

Received 6th August 2017,  
Accepted 18th September 2017

DOI: 10.1039/c7dt02901b

[rsc.li/dalton](http://rsc.li/dalton)


## Introduction

Metal macroheterocycles are effective components for the design of optical, magnetic and conducting materials. Some phthalocyanine (Pc) and porphyrin (Porph) derivatives can be used as sensors, as materials for optical and electronic devices, and in photoelectronics.<sup>1</sup> Conducting compounds were obtained by the oxidation of free-base and metal-containing phthalocyanines using iodine or the electrochemical oxidation of axially substituted phthalocyanine [ $\text{M}^{\text{III}}\text{PcL}_2$ ]<sup>−</sup> anions ( $\text{M} = \text{Co}, \text{Fe}; \text{L} = \text{CN}, \text{Cl}, \text{Br}$ ).<sup>2</sup> Since metal phthalocyanines can contain paramagnetic metals, they have also been used as active components in the design of magnetic assemblies.<sup>3</sup> For example, polymeric compounds with alternating  $(\text{Mn}^{\text{III}}\text{Pc})^+$  or

$(\text{Mn}^{\text{III}}\text{Porph})^+$  and tetracyanoethylene ( $\text{TCNE}^{\cdot-}$ ) ions show ferromagnetic ordering of spins.<sup>3a,b</sup> The reduction of iron(II) phthalocyanine using decamethylchromocene ( $\text{Cp}^*\text{Cr}$ ) allows one to obtain the complex with  $\pi$ -stacks of alternating  $[\text{Fe}^{\text{I}}(\text{Pc}^{2-})]^-$  ( $S = 1/2$ ) and  $\text{Cp}^*\text{Cr}^+$  ( $S = 3/2$ ) ions which shows ferrimagnetic ordering of spins below 5 K.<sup>3c</sup> The charge transfer complex  $(\text{Cp}^*\text{Cr}^+)(\text{H}_2\text{Pc}^{\cdot-})\cdot 4\text{C}_6\text{H}_4\text{Cl}_2$  of free-base phthalocyanine ( $\text{H}_2\text{Pc}$ ) with  $\text{Cp}^*\text{Cr}$  has similar  $\pi$ -stacks of alternating ions but no essential magnetic coupling was found in this complex (the Weiss temperature is  $-4$  K) most probably due to ineffective  $\pi$ - $\pi$  interactions between  $\text{H}_2\text{Pc}^{\cdot-}$  and the  $\text{Cp}^*$  ligand.<sup>3d</sup> Nevertheless, this work shows that free-base macroheterocycles can also be used in the design of magnetic assemblies.

*meso*-Substituted 5,10,15-triarylcorroles ( $\text{H}_3\text{TArlylCor}$ ) are related to *meso*-substituted 5,10,15,20-tetraarylporphyrins but one aryl-C fragment is removed from the macrocycle (Scheme 1).<sup>4</sup> Free-base triarylcorroles have complicated reduction chemistry.<sup>5</sup> They are reduced in benzonitrile (BN) at about  $-1.03$  V vs. SCE (for aryl =  $\text{Ph}(\text{CF}_3)_2$ ) but this reduction is accompanied by deprotonation and the formation of the  $\text{H}_2\text{TArlylCor}^-$  anions. The deprotonation becomes easier in basic solvents like pyridine (Py) and the  $\text{H}_2\text{TArlylCor}^-$  anions are formed under these conditions even without reduction in

<sup>a</sup>Institute of Problems of Chemical Physics RAS, Chernogolovka, Moscow region, 142432 Russia. E-mail: konarev3@yandex.ru<sup>b</sup>Institute of Solid State Physics RAS, Chernogolovka, Moscow region, 142432 Russia<sup>c</sup>Division of Chemistry, Graduate School of Science, Kyoto University, Sakyo-ku, Kyoto 606-8502, Japan<sup>d</sup>Research Center for Low Temperature and Materials Sciences, Kyoto University, Sakyo-ku, Kyoto 606-8501, Japan<sup>†</sup>Electronic supplementary information (ESI) available. CCDC 1552215 and 1552216. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c7dt02901b

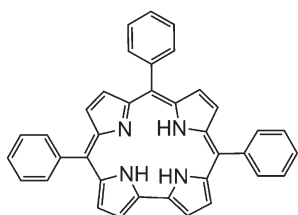5, 10, 15-triphenylcorrole ( $H_3TPCor$ )

Scheme 1

some cases. Therefore, the  $H_3TPCor^{\cdot-}$  radical anions are not stable in solution due to deprotonation. Nevertheless, paramagnetic radical  $H_2TPCor^{\cdot-}$  dianions can be obtained by the reduction of the  $H_2TPCor^-$  anions at  $-1.40$  V in BN and at  $-1.60$  V in Py vs. SCE.<sup>5</sup> Decamethylchromocene with  $E_{ox} = -1.04$  V vs. SCE in  $CH_3CN$  has strong donor properties<sup>6</sup> and potentially can generate anionic species of 5,10,15-triarylcorroles. Now corroles and their metal complexes have been intensively studied in different fields<sup>4</sup> but anionic species of these macrocycles neither have been obtained nor studied in solid form so far. The  $H_2TPCor^-$  and  $H_2TPCor^{\cdot-}$  anions were only generated by the electrochemical reduction of free-base triarylcorroles in BN or Py and their optical properties were studied in solution.<sup>5</sup>

In this work, we obtained the first crystalline charge transfer complex of free-base 5,10,15-triphenylcorrole with decamethylchromocene ( $Cp^*_2Cr^+(H^+)(H_2TPCor^{\cdot-}) \cdot C_6H_4Cl_2$  (**1**)) and analyzed its structure, and optical and magnetic properties.  $Cp^*_2Cr$  reduces a free-base corrole but the  $H_3Cor^{\cdot-}$  radical anion loses a proton to form the  $H_2TPCor^{\cdot-}$  radical dianions. Alternation of two paramagnetic  $Cp^*_2Cr^+$  and  $H_2TPCor^{\cdot-}$  ions in the  $\pi$ -stacks of **1** provides rather effective magnetic coupling between them. To understand the difference between reduced and deprotonated ( $H_2TPCor^{\cdot-}$ ) and deprotonated ( $H_2TPCor^-$ ) anions, we also obtained the crystalline {cryptand[2,2,2]( $Na^+$ )}( $H_2TPCor^-$ ) $\cdot 0.5C_6H_4Cl_2$  (**2**) salt. The comparison of these anions shows that they have different optical and magnetic properties.

## Results and discussion

Starting  $H_3TPCor$  was synthesized<sup>8</sup> by the benzaldehyde-pyrrole condensation in the water-methanol mixture in the presence of HCl followed by oxidative cyclization using *p*-chloranil in boiling chloroform. The product was purified by column chromatography.  $H_3TPCor$  is well soluble in *o*-dichlorobenzene to produce a blue-green solution. The addition of an excess of  $Cp^*_2Cr$  under anaerobic conditions resulted in a color change to red-green. Slow mixing of the obtained solution with *n*-hexane over 1.5 months precipitated crystals on the walls of the diffusion tube. The solvent was decanted and crystals were washed with *n*-hexane to give elongated black planks in 43% yield. The crystals are very air sensitive, and their com-

position determined from X-ray diffraction on a single crystal is  $(Cp^*_2Cr^+)(H^+)(H_2TPCor^{\cdot-}) \cdot C_6H_4Cl_2$  (**1**). Hydrogen atoms bonded to nitrogen cannot be unambiguously localized in the structure analysis of **1**. Nevertheless, the attempts to geometrically insert three hydrogen atoms in the planar corrole macrocycle result in very short H...H contacts between them (less than  $1.4$  Å). Hence, we suppose that only two hydrogen atoms remain in the center of the macrocycle and the third proton is removed. Starting  $H_3TPCor$  is stable in *o*-dichlorobenzene and interaction with  $Cp^*_2Cr$  should provide the  $H_3TPCor^{\cdot-}$  radical anion which is not stable and loses a proton to form the radical  $H_2TPCor^{\cdot-}$  dianion. Deprotonated  $H_2TPCor^-$  anions are not formed in **1** as we show below. To obtain salt **2** with the  $H_2TPCor^-$  anions,  $H_3TPCor$  was deprotonated by NaOH in *o*-dichlorobenzene in the presence of one equivalent of cryptand[2,2,2]. In spite of the fact that NaOH is completely insoluble in this solvent, cryptand[2,2,2] forms a stable complex with  $Na^+$  allowing exactly one equivalent of NaOH to be dissolved to deprotonate  $H_3TPCor$  and form greenish brown solution with the  $H_2TPCor^-$  anions. Slow mixing of the obtained solution with *n*-hexane over one month produced black blocks of {cryptand[2,2,2]( $Na^+$ )}( $H_2TPCor^-$ ) $\cdot 0.5C_6H_4Cl_2$  (**2**) whose composition was determined from X-ray diffraction analysis on a single crystal and was confirmed by elemental analysis (ESI†).

The solid state spectra of  $H_3TPCor$ , **1** and **2** in the UV-visible-NIR range are shown in Fig. 1. Starting  $H_3TPCor$  manifests absorption bands at  $424$  nm (the Soret band) and the split Q-band in the visible range at  $575$ ,  $618$  and  $662$  nm (Fig. 1a). Deprotonation results in essential modification of the optical spectrum. For **2**, the intense Soret band is split into two bands positioned at  $432$  and  $450$  nm and the Q-band ( $537$ ,  $597$  and  $647$  nm) becomes more pronounced since the intensity of the lowest energy band at  $647$  nm increases strongly (Fig. 1b). The spectra of deprotonated triarylcorrole anions ( $H_2TPCor^-$ ) in Py show very similar features in the visible range including strongly increased intensity of the band at

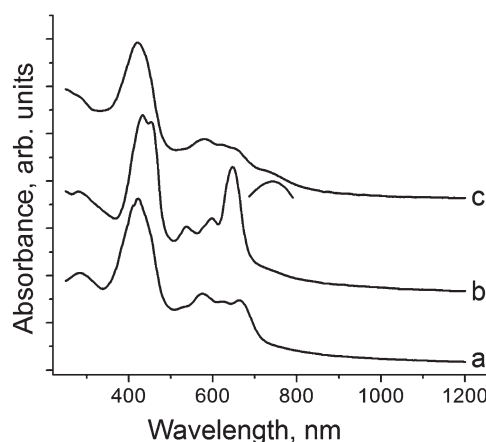


Fig. 1 Spectra of starting  $H_3TPCor$  (a); salt {cryptand[2,2,2]( $Na^+$ )}( $H_2TPCor^-$ ) $\cdot 0.5C_6H_4Cl_2$  (**2**) (b); and complex  $(Cp^*_2Cr^+)(H^+)(H_2TPCor^{\cdot-}) \cdot C_6H_4Cl_2$  (**1**) (c) in the UV-visible-NIR range measured in KBr pellets prepared under anaerobic conditions.



643 nm.<sup>5</sup> However, the Soret band remains unsplit in the solution spectra of  $\text{H}_2\text{TArlylCor}^-$  and is observed at 439–440 nm<sup>5</sup> (its position is approximately intermediate between 432 and 450 nm).

The solid state spectrum of **1** differs from that of **2**. It shows an intense Soret band at 421 nm and split Q-bands at 579, 614 and 644 nm (Fig. 1c). The band at 644 nm is of essentially lower intensity (Fig. 1c) than that in the spectrum of **2**. The lowest energy band in the spectrum of **1** is observed as a shoulder with an approximate maximum at 750 nm (shown by an arc in Fig. 1c). On the whole, the spectrum of **1** is similar to that of electrochemically generated radical  $\text{H}_2\text{TArlylCor}^{2-}$  dianions which shows a Soret band at 418 nm, relatively weak bands at 570–650 nm and the lowest energy band at 755 nm.<sup>5</sup> Thus, the optical spectra allow one to suppose the formation of  $\text{H}_2\text{TPCor}^{2-}$  and  $\text{H}_2\text{TPCor}^-$  anions in **1** and **2**, respectively, and their spectra are to a certain extent similar to the solution spectra of these anions.<sup>5</sup>

The crystal structures of **1** and **2** were analyzed at 110 K. The  $\text{H}_3\text{TPCor}$  macrocycles have a smaller coordination core in comparison with porphyrins, and the presence of three hydrogen atoms in this core results in essential repulsion between them. To avoid short  $\text{H}\cdots\text{H}$  contacts, the macrocycle in a neutral state adopts a strongly nonplanar conformation.<sup>9</sup> In contrast, the corrole macrocycle in  $\text{H}_2\text{TPCor}^{2-}$  is nearly planar in **1** with a slight deviation of only pyrrole nitrogen atoms from the 23-atom plane by 0.029–0.185 Å (Fig. 2a and b). Three hydrogen atoms cannot be inserted into the center of the planar corrole macrocycle due to very short  $\text{H}\cdots\text{H}$  contacts (less than 1.4 Å). Therefore, we suppose that only two hydrogen atoms are preserved in  $\text{H}_2\text{TPCor}^{2-}$ . In this case, the  $\text{H}\cdots\text{H}$  distance of 2.152 Å indicates the absence of noticeable repulsion between hydrogen atoms. Most probably, the third proton can be localized in the structure of **1** as a counter cation.

The  $\text{H}_2\text{TPCor}^{2-}$  radical dianions and the  $\text{Cp}^*_2\text{Cr}^+$  cations form  $\pi$ -stacking columns along the *b* axis (Fig. 2a and b). There is effective overlapping between the corrole and the  $\text{Cp}^*$  ligand in **1** since the interplanar distance between them is only 3.42 Å and a dihedral angle is 0.95°. As a result, multiple van der Waals  $\text{C},\text{N}\cdots\text{C},\text{N}$  contacts are formed between them in the 3.44–3.56 Å range. The relative orientation of half of the  $\text{Cp}^*_2\text{Cr}^+$  cations to the TPCor macrocycle is shown in Fig. 2c. The  $\text{Cp}^*_2\text{Cr}^+$  cations have a staggered conformation in **1** typical of decamethylmetallocenes. The average  $\text{Cr}-\text{C}(\text{Cp}^*)$  bond length is 2.201(5) Å. This value is close to that of the  $\text{Cp}^*_2\text{Cr}^+$  cations (the average  $\text{Cr}-\text{C}(\text{Cp}^*)$  bond length is 2.176(3)–2.198(3) Å).<sup>3c,d,11</sup> These bonds are noticeably longer than those in neutral  $\text{Cp}^*_2\text{Cr}$  (2.152(4) Å<sup>12</sup>).

The deprotonation of  $\text{H}_3\text{TPCor}$  in **2** also provides a nearly planar shape of the  $\text{H}_2\text{TPCor}^-$  macrocycle since all atoms are positioned in the 23-atom corrole plane with maximal deviations of pyrrole nitrogen atoms by 0.005–0.110 Å. No essential repulsion is observed between the hydrogen atoms of  $\text{H}_2\text{TPCor}^-$  due to the 2.308–2.352 Å distances between them. Therefore, repulsion between the three hydrogen atoms of  $\text{H}_3\text{TPCor}$  is a reason for the non-planar shape of neutral free-base corrole macrocycles. Deprotonation restores its planar shape. Corrole planes form channels in **2** occupied by bulky cryptand[2,2,2]( $\text{Na}^+$ ) cations and arranged approximately along the *a* axis (Fig. S2†).

Previously, the alternation of the  $\text{C}-\text{N}(\text{imine})$  and  $\text{C}-\text{C}$  (*meso*) bonds was found for the reduced phthalocyanine macrocycles in  $\text{H}_2\text{Pc}^{3-}$  and  $\{\text{M}(\text{Pc}^{3-})\}^-$  and for the porphyrin radical trianions in  $\text{Al}^{\text{III}}(\text{THF})_2(\text{Porph}^{3-})$ , respectively.<sup>3d,7,10</sup> This alternation is realized in the  $\text{H}_2\text{Pc}^{3-}$  radical anions (Fig. 4a) by such a way that short and long bonds belong to two oppositely located isoindole units. The difference between the short and long bonds is about 0.04 Å. This

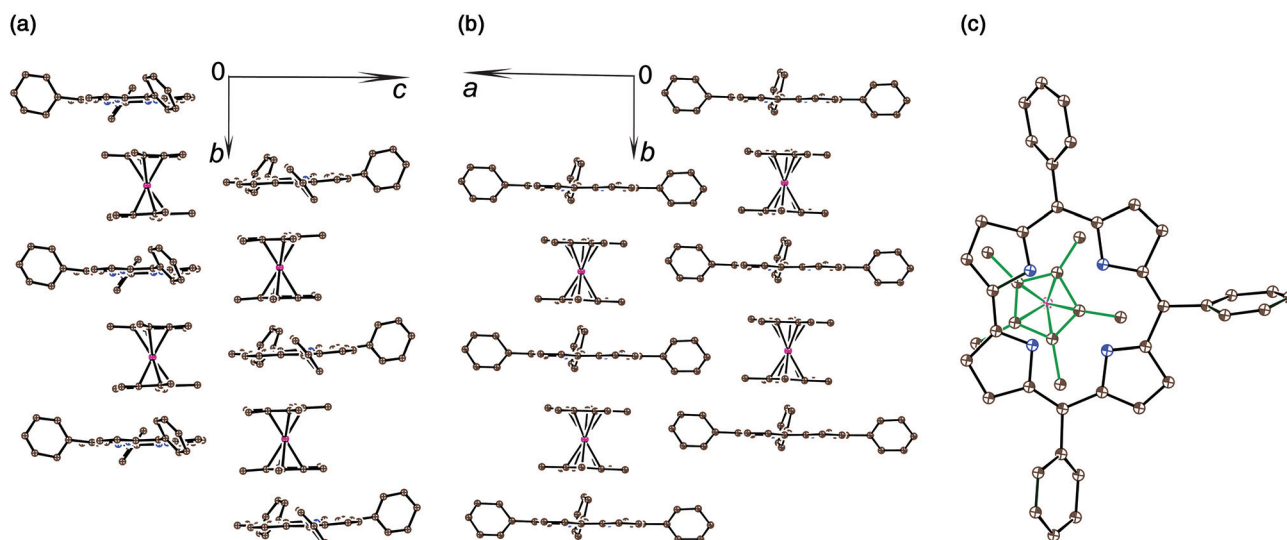



Fig. 2 Crystal structure of complex **1**: views on the  $\pi$ -stacks of alternating radical  $\text{H}_2\text{TPCor}^{2-}$  dianions and the  $\text{Cp}^*_2\text{Cr}^+$  cations along the *a*- (a) and *c*-axes (b); projection of one half of the  $\text{Cp}^*_2\text{Cr}^+$  cations (bonds are shown by green lines) on the TPCor plane (c). Hydrogen atoms are not shown.




**Fig. 3** Bond length, position and occupancy (in parentheses) of hydrogen atoms in the center of the macrocycle for: (a) pristine H<sub>3</sub>TPCor according to ref. 3; (b) deprotonated H<sub>2</sub>TPCor<sup>−</sup> anion in {cryptand[2,2,2](Na<sup>+</sup>)}(H<sub>2</sub>TPCor<sup>−</sup>)·0.5C<sub>6</sub>H<sub>4</sub>Cl<sub>2</sub> (**2**) with two hydrogen atoms occupying four positions with the 0.58/0.42 occupancies; and (c) the radical H<sub>2</sub>TPCor<sup>·2−</sup> dianion in (Cp<sup>+</sup><sub>2</sub>Cr<sup>+</sup>)(H<sup>+</sup>)(H<sub>2</sub>TPCor<sup>·2−</sup>)·C<sub>6</sub>H<sub>4</sub>Cl<sub>2</sub> (**1**). Phenyl substituents of TPCor are omitted.

alternation is explained by the partial disruption of aromaticity of the Pc macrocycle during the transition from a stable 18  $\pi$ -electron system of  $\text{H}_2\text{Pc}$  to a less stable 19  $\pi$ -electron system of  $\text{H}_2\text{Pc}^{+\cdot}$ .<sup>3d,7</sup> The lengths of the C-C and C-N bonds in neutral  $\text{H}_3\text{TPCor}$ ,<sup>9</sup>  $\text{H}_2\text{TPCor}^-$  and  $\text{H}_2\text{TPCor}^{2-}$  are shown in Fig. 3. It is seen that the alternation of the C-C(*meso*) bonds is also observed in  $\text{H}_2\text{TPCor}^{2-}$  with the appearance of short and long bonds (Fig. 4b). The short and long bonds are positioned similarly to those in  $\text{H}_2\text{Pc}^{+\cdot}$  (Fig. 4a) but one short bond is absent in  $\text{H}_2\text{TPCor}^{2-}$  (Fig. 4). The difference between the short and long bonds for  $\text{H}_2\text{TPCor}^{2-}$  (0.02 Å) is about two times smaller than that for  $\text{H}_2\text{Pc}^{+\cdot}$  (0.04 Å). The alternation is not observed for the deprotonated  $\text{H}_2\text{TPCor}^-$  anion (Fig. 3b) as well as for the deprotonated  $\text{HPc}^-$  anion<sup>7</sup> due to the preservation of 18  $\pi$ -electron systems in these anions. At the same time, pristine  $\text{H}_3\text{TPCor}$  also shows some alternation of the C-C(*meso*) bonds (Fig. 3a). Since  $\text{H}_3\text{TPCor}$  has a strong non-planar shape due to the repulsion of hydrogen atoms, we suppose that the partial disruption of aromaticity is also possible in this macrocycle.

Fig. 5 shows the calculated structures of the *meso*-substituted H<sub>3</sub>TPCor macrocycle (a), its deprotonated form (b), the structure of the H<sub>2</sub>TPCor<sup>2-</sup> macrocycle in the (H<sub>2</sub>TPCor<sup>2-</sup>) (Cp\*<sub>2</sub>Cr<sup>+</sup>) complex (c) and the H<sub>2</sub>Cor<sup>2-</sup> radical dianion (d) (see

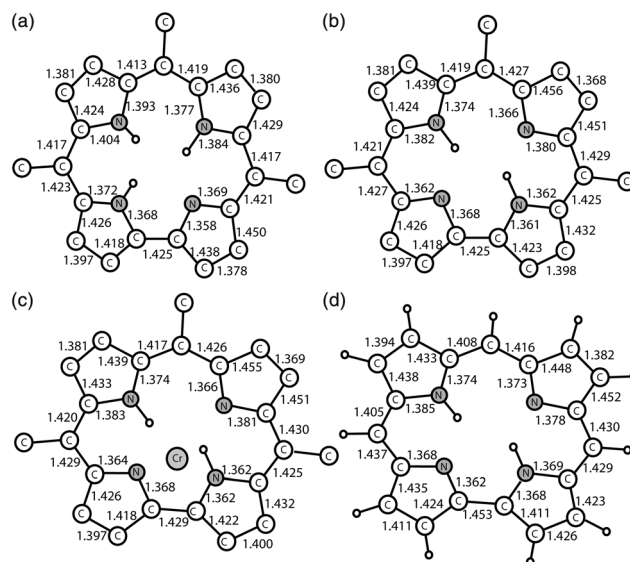

**Fig. 5** Calculated structures of pristine  $\text{H}_3\text{TPCoR}$  (a), the deprotonated  $\text{H}_2\text{TPCoR}^-$  anion (b); the  $\text{H}_2\text{TPCoR}^{2-}$  radical dianion in the  $(\text{H}_2\text{TPCoR}^{2-})$  ( $\text{Cp}^*\text{Cr}^+$ ) complex (c) and the  $\text{H}_2\text{CoR}^{2-}$  radical dianion for comparison (d).

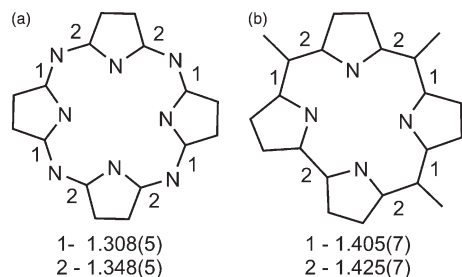

**Fig. 4** (a) Alternation of the C–N(imine) bonds in the  $\text{H}_2\text{Pc}^{\cdot-}$  radical anions according to ref. 7; (b) Alternation of the C–C(meso) bonds in the  $\text{H}_2\text{TPCor}^{\cdot 2-}$  radical dianions in **1**. The lengths of short (type 1) and long (type 2) bonds are also shown.

the ESI† for details). The calculated structure of isolated H<sub>2</sub>TPCo<sup>r</sup> (Fig. 5a) is in good agreement with the experimental data of the molecular crystal (Fig. 3a). The average values of the C–N and C–C bonds are greater than the experimental values by 0.002 and 0.007 Å, respectively. This difference remains at the same level for the deprotonated H<sub>2</sub>TPCo<sup>r−</sup> anion (Fig. 5b). The geometry of the H<sub>2</sub>TPCo<sup>r•2−</sup> radical dianion was calculated in the complex with Cp\*<sub>2</sub>Cr<sup>+</sup> to take into account the Coulomb field of the surrounding counterions (Fig. 5c). In this structure, only a small change of the mean values of the C–N and C–C bonds of 0.001 (−0.006) and 0.000 (0.000) Å, respectively, is observed (the experimental values are given in parentheses). In contrast, the larger divergence of the C–N and C–C bonds is observed in the calculated structure of isolated H<sub>2</sub>TPCo<sup>r•2−</sup> (Fig. S3†), 0.012 and 0.021 Å, respectively, with respect to the

experimental data. This calculation indicates an increase of the difference between the short and long C–C(*meso*) bonds in the macrocycle during the transition from  $\text{H}_2\text{TPCor}^-$  to  $\text{H}_2\text{TPCor}^{2-}$  from 0.060 (0.006) to 0.010 (0.020) Å (the experimental values are given in parentheses).


The comparison of the geometry of the radical  $\text{H}_2\text{Cor}^{2-}$  and  $\text{H}_2\text{TPCor}^{2-}$  dianions (Fig. 5d and 5c, respectively) shows that the introduction of phenyl groups results in the systematic elongation of C–C(*meso*) bonds by 0.005 Å as the average. The excess electron in the radical dianions appears on the antibonding  $\pi$ -orbitals. As we discussed above for  $\text{H}_2\text{Pc}^-$  that provides the alternation of the C–C(*meso*) bonds due to partial disruption of the macrocycle aromaticity. The main geometric differences between  $\text{H}_2\text{Cor}^{2-}$  and  $\text{H}_2\text{TPCor}^{2-}$  are due to the stronger alternation of the C–C(*meso*) bonds for  $\text{H}_2\text{Cor}^{2-}$  (0.018 Å) than that for  $\text{H}_2\text{TPCor}^{2-}$  (0.010 Å). In fact, that is a consequence of a different electron density distribution for the *meso*-substituted form since approximately half of the additional negative charge in  $\text{H}_2\text{TPCor}^{2-}$  is distributed among the phenyl substituents. As a result, the effect of population of the antibonding  $\pi$ -orbitals on the macrocycle decreases. This effect can decrease the alternation of the C–C(*meso*) bonds in  $\text{H}_2\text{TPCor}^{2-}$  in comparison with  $\text{H}_2\text{Cor}^{2-}$  and even  $\text{H}_2\text{Pc}^-$ . A similar effect is observed for the  $\{\text{Cu}^{\text{II}}(\text{F}_{16}\text{Pc}^{3-})\}^{\cdot-}$  radical anions in which an excess of negative charge is to a great extent delocalized among the acceptor fluoro-substituents.<sup>13</sup> Another anomaly is the significant difference in the lengths of the C–N bonds within one pyrrole ring of  $\text{H}_2\text{TPCor}^{2-}$  in **1**, reaching 0.054 Å (Fig. 3c). The common reason for this phenomenon is the lability of the electron system of the radical dianion and the significant effect of the Coulomb field of the surrounding counterions.

Two counter cations are required for the electroneutrality of **1** with the radical  $\text{H}_2\text{TPCor}^{2-}$  dianions. One cation is  $\text{Cp}^*\text{Cr}^+$  and the other cation should be  $\text{H}^+$  removed from the macrocycle. The reaction was carried out under very dry conditions and in a base (B) free medium to stabilize  $\text{H}^+$  in the hydronium ( $\text{H}_3\text{O}^+$ ) or  $\text{HB}^+$  cations (residual electron density in **1** is too small (0.87 e) to be attributed to  $\text{H}_3\text{O}^+$ ). Therefore, most probably, the proton is localized somewhere in the structure of **1**. One of the possible positions is near the two chloride substituents of  $o\text{-C}_6\text{H}_4\text{Cl}_2$ . In this case, the Cl– $\text{H}^+$  distance would be about 1.715 Å, which is reasonable for the interaction of such a type. The  $(\text{Cl}\cdots\text{H}\cdots\text{Cl})^-$  anions with strong  $(\text{Cl}^-)\cdots(\text{H}^+)$  hydrogen bonds are known and have close Cl– $\text{H}^+$  distances of 1.56–1.64 Å.<sup>14</sup> According to our calculations, the binding of a proton to  $o\text{-C}_6\text{H}_4\text{Cl}_2$  leads to the formation of strong  $\text{Cl}\cdots(\text{H}^+)$  hydrogen bonds of 1.573 Å length and the elongation of the C–Cl bonds in this molecule by about 0.036 Å. These data agree with the experimental results since the C–Cl bonds for the  $o\text{-C}_6\text{H}_4\text{Cl}_2$  molecules in **1** forming hydrogen bonds with  $\text{H}^+$  are elongated by 0.03 Å in comparison with those for the non-bonded  $o\text{-C}_6\text{H}_4\text{Cl}_2$  molecules. In addition, the formation of strong  $\text{Cl}\cdots(\text{H}^+)$  hydrogen bonds leads to the appearance of new broad absorption bands in the theoretical IR spectrum at 770 and 1050  $\text{cm}^{-1}$ . Indeed, broad bands are observed at

about 800 and 1040  $\text{cm}^{-1}$  in the experimental IR spectrum of **1** (Fig. S1†). The calculation of the structure of the  $\text{H}_3\text{TPCor}^-$  radical anion shows its nonplanar character as expected. This calculation allows one to find the proton affinity for the  $\text{H}_2\text{TPCor}^{2-}$  radical dianion which is equal to 16.8 eV. This value significantly exceeds the affinity for the proton of the  $o\text{-C}_6\text{H}_4\text{Cl}_2$  molecule, 7.2 eV. A logical question arises is to how such a weak base as  $o\text{-C}_6\text{H}_4\text{Cl}_2$  can hold a proton in the presence of a stronger  $\text{H}_2\text{TPCor}^{2-}$  base. One of the explanations is that the acceptance of the proton by the  $o\text{-C}_6\text{H}_4\text{Cl}_2$  molecule is energetically favorable due to the gain in the Coulomb energy for the crystal lattice.

The magnetic properties of **1** were studied by EPR and SQUID techniques. The effective magnetic moment is equal to  $4.10\mu_{\text{B}}$  at 300 K (Fig. 6a), which is close to the calculated magnetic moment for a system of non-interacting  $S = 3/2$  spins from  $\text{Cp}^*\text{Cr}^+$  and  $S = 1/2$  spins from  $\text{H}_2\text{TPCor}^{2-}$  ( $\mu_{\text{eff}} = 4.24\mu_{\text{B}}$ ). The magnetic moment decreases below 120 K (Fig. 6a) most probably due to the antiferromagnetic coupling of spins. The reciprocal molar magnetic susceptibility of **1** is linear in the 50–300 K range allowing the Weiss temperature to be determined as –31 K (Fig. 6b). This value indicates a strong antiferromagnetic coupling of spins in the  $\pi$ -stacks containing alternating  $\text{Cp}^*\text{Cr}^+$  and  $\text{H}_2\text{TPCor}^{2-}$  ions. However, long-range magnetic ordering is not observed in **1** down to 1.9 K. It should be noted that the observed magnetic coupling in **1** is essentially stronger than that in the previously studied  $(\text{Cp}^*\text{Cr}^+)(\text{H}_2\text{Pc}^-)\cdot 4\text{C}_6\text{H}_4\text{Cl}_2$  complex with free-base phthalocyanine radical anions which also contains  $\pi$ -stacks of alternating  $\text{Cp}^*\text{Cr}^+$  and  $\text{H}_2\text{Pc}^-$  ions.<sup>3d</sup> From this viewpoint, free-base corroles can be more effective magnetic mediators than free-base phthalocyanines.

The EPR spectra of polycrystalline **1** confirm the presence of two paramagnetic species. An intense and relatively narrow signal is observed at 323–325 mT. This signal contains two

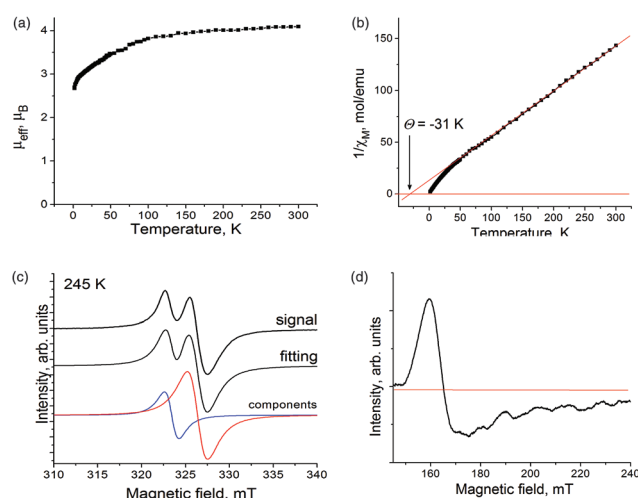

**Fig. 6** Magnetic data of **1**: temperature dependencies of the effective magnetic moment (a) and reciprocal molar magnetic susceptibility (b). EPR signals are attributed to the  $\text{H}_2\text{TPCor}^{2-}$  dianions (c) and the  $\text{Cp}^*\text{Cr}^+$  cations with the  $S = 3/2$  spin state (d).



lines with  $g_1 = 1.9971$  and the linewidth ( $\Delta H$ ) of 1.58 mT and  $g_2 = 1.9790$  and  $\Delta H = 2.28$  mT at 292 K (Fig. 6c shows this signal at 245 K) and can be attributed to the paramagnetic radical  $\text{H}_2\text{TPCor}^{\cdot 2-}$  dianions. Both signals are preserved down to 4.2 K. Below 90 K, the abrupt decrease of  $g$ -factors is observed, and both lines are broadened and shifted to higher  $g$ -factor values at  $T < 30$  K (Fig. S4a and S4b†) due to the anti-ferromagnetic coupling of spins. Obviously, both lines originate from the same paramagnetic species since they show similar temperature dependencies of  $g$ -factors and linewidths (Fig. S4a and S4b†). It should be noted that the EPR signal from  $\text{H}_2\text{TPCor}^{\cdot 2-}$  is broader ( $\Delta H = 1.5\text{--}2.3$  mT) than those from the  $\text{H}_2\text{Pc}^{\cdot -}$  radical anions ( $\Delta H = 0.2\text{--}0.6$  mT).<sup>3d,10a,b</sup> At the same time, complex **1** as well as the  $\text{H}_2\text{Pc}^{\cdot -}$  salts do not display the super hyperfine splitting characteristic of some oxidized porphyrins and explained by the interaction of spins with four coordinated nitrogen atoms.<sup>15</sup> Most probably, the measurement of the diluted samples is needed to observe such splitting.

The  $\text{Cp}^*\text{Cr}^+$  cations show a broad asymmetric EPR signal with the main component at  $g_3 = 3.88$  and  $\Delta H = 12.0$  mT at 292 K (signal at 245 K is shown in Fig. 3d). The strong asymmetry of the signal could be explained by the polycrystallinity of the sample. Generally, the  $\text{Cp}^*\text{Cr}^+$  cations with the  $S = 3/2$  spin state manifest similar EPR signals in the complexes with different anions, and the strong asymmetry of the signal is also observed in some cases.<sup>16</sup> The signal from  $\text{Cp}^*\text{Cr}^+$  has a nearly temperature independent  $g$ -factor and a linewidth down to 4.2 K.

Crystals of **2** were also studied by the EPR technique at room temperature and at 4.2 K. They are EPR silent at both temperatures due to the diamagnetism of deprotonated  $\text{H}_2\text{TPCor}^{\cdot -}$  anions. Similarly, the deprotonated  $\text{HPc}^{\cdot -}$  anions were diamagnetic and EPR silent.<sup>7</sup> The removal of one proton from the macrocycle does not change the number of  $\pi$ -electrons and preserves the diamagnetic state of the macrocycle.

## Experimental

### Materials

Free-base 5,10,15-triphenylcorrole ( $\text{H}_3\text{TPCor}$ ) was synthesized according to ref. 8. Decamethylchromocene ( $\text{Cp}^*\text{Cr}$ , >95%) was purchased from Strem. Cryptand[2,2,2] was purchased from TCI Reagents. *o*-Dichlorobenzene ( $\text{C}_6\text{H}_4\text{Cl}_2$ , Acros) was distilled over  $\text{CaH}_2$  under reduced pressure and *n*-hexane was distilled over Na/benzophenone. Solvents were degassed and stored in an MBraun 150B-G glove box. Salt **1** was synthesized and stored in the glove box under a controlled atmosphere containing less than 1 ppm of water and oxygen. KBr pellets used for the IR and UV-visible-NIR analyses were prepared in the glove box. Magnetic measurements were performed on polycrystalline samples of **1** and **2** sealed in a 2 mm quartz tube in anaerobic conditions under ambient pressure.

### General

UV-visible-NIR spectra were recorded in KBr pellets on a PerkinElmer Lambda 1050 spectrometer in the 250–2500 nm

range. FT-IR spectra were obtained in KBr pellets on a PerkinElmer Spectrum 400 spectrometer ( $400\text{--}7800\text{ cm}^{-1}$ ). EPR spectra were recorded for a polycrystalline sample of **1** from room temperature (RT) down to 4.2 K and for a polycrystalline sample of **2** at RT and 4.2 K on a JEOL JES-TE 200 X-band ESR spectrometer equipped with a JEOL ES-CT470 cryostat. A Quantum Design MPMS-XL SQUID magnetometer was used to measure the static magnetic susceptibility of **1** at 100 mT magnetic field under cooling and heating conditions in the 300–1.9 K range. A sample holder contribution and core temperature independent diamagnetic susceptibility ( $\chi_d$ ) were subtracted from the experimental values. The  $\chi_d$  values were estimated by the extrapolation of the data in the high-temperature range by fitting the data using the following expression:  $\chi_M = C/(T - \Theta) + \chi_d$ , where  $C$  is the Curie constant and  $\Theta$  is the Weiss temperature. The effective magnetic moment ( $\mu_{\text{eff}}$ ) was calculated using the following formula:  $\mu_{\text{eff}} = (8\chi_M T)^{1/2}$ .

### Synthesis

Crystals of **1** and **2** were obtained by the diffusion technique. A reaction mixture was filtered into a 1.8 cm-diameter, 50 mL glass tube with a ground glass plug, and then 30 mL of *n*-hexane was layered over the solution. Slow mixing of the solutions resulted in the precipitation of crystals over 1–1.5 months. The solvent was then decanted from the crystals, and they were washed with *n*-hexane. The composition of the obtained compound was determined from X-ray diffraction analysis on a single crystal. Several crystals from one synthesis were found to consist of a single crystalline phase.

Crystals of  $(\text{Cp}^*\text{Cr}^+)(\text{H}^+)(\text{H}_2\text{TPCor}^{\cdot 2-})\cdot\text{C}_6\text{H}_4\text{Cl}_2$  (**1**) were obtained *via* the reaction of  $\text{H}_3\text{TPCor}$  (22 mg, 0.042 mmol) with an excess of  $\text{Cp}^*\text{Cr}$  (20 mg, 0.0562 mmol) in 16 mL of *o*-dichlorobenzene upon stirring at 80 °C for 24 hours. The color of the solution changed from blue-green to red-green. The obtained solution was cooled down to room temperature and filtered into the tube for diffusion. Black planks of **1** were obtained in 43% yield.

$\{\text{Cryptand}[2,2,2](\text{Na}^+)\}(\text{H}_2\text{TPCor}^{\cdot -})\cdot 0.5\text{C}_6\text{H}_4\text{Cl}_2$  (**2**) was obtained *via* the reaction of  $\text{H}_3\text{TPCor}$  (22 mg, 0.042 mmol) with an excess of powdered NaOH (30 mg, 0.75 mmol) and one equivalent of cryptand[2,2,2] (16 mg, 0.042 mmol) in 16 mL of *o*-dichlorobenzene upon stirring at 80 °C for 24 hours. The color of the solution changed from blue-green to greenish brown. The obtained solution was cooled down to RT and filtered into the tube for diffusion. Black blocks of **2** were obtained in 79% yield. The composition of **2** was determined from X-ray diffraction on a single crystal and was confirmed *via* elemental analysis: anal. calcd for  $\text{C}_{58}\text{H}_{63}\text{ClN}_6\text{NaO}_6$ ,  $M_r = 998.58$ ; C 69.76, H 6.30, N 8.41, Cl 3.55; found: C 69.54, H 6.24, N 8.21, Cl 3.36.

### X-ray crystal structure determination

Crystal data of **1** at 110(1) K:  $\text{C}_{63}\text{H}_{59}\text{Cl}_2\text{CrN}_4$ ,  $M_r = 995.04\text{ g mol}^{-1}$ , black plank, monoclinic,  $C2/c$ ,  $a = 26.245(3)$ ,  $b = 10.6383(6)$ ,  $c = 36.765(3)\text{ \AA}$ ,  $\beta = 90.065(8)^\circ$ ,  $V = 10\,265.0(15)\text{ \AA}^3$ ,  $Z = 8$ ,  $d_{\text{calc}} = 1.288\text{ g cm}^{-3}$ ,  $\mu = 0.372\text{ mm}^{-1}$ ,  $F(000) = 4184$ ,



$2\theta_{\max} = 52.742^\circ$ , reflections measured 44 240, unique reflections 9723, reflections with  $I > 2\sigma(I) = 5747$ , parameters refined 669, restraints 271,  $R_1 = 0.0787$ ,  $wR_2 = 0.1959$ , G.O.F. = 1.015, CCDC 1552215.†

Crystal data of **2** at 110(1) K:  $C_{58}H_{63}ClN_6NaO_6$ ,  $M_r = 998.58 \text{ g mol}^{-1}$ , black block, monoclinic,  $P2_1/n$ ,  $a = 13.0302(2)$ ,  $b = 18.0323(3)$ ,  $c = 21.3928(4) \text{ \AA}$ ,  $\beta = 96.142(2)^\circ$ ,  $V = 4997.69(15) \text{ \AA}^3$ ,  $Z = 4$ ,  $d_{\text{calc}} = 1.327 \text{ g cm}^{-3}$ ,  $\mu = 0.145 \text{ mm}^{-1}$ ,  $F(000) = 2116$ , max.  $2\theta_{\max} = 54.206^\circ$ , reflections measured 55 350, unique reflections 11 012, reflections with  $I > 2\sigma(I) = 9172$ , parameters refined 674, restraints 246,  $R_1 = 0.0462$ ,  $wR_2 = 0.1332$ , G.O.F. = 1.032, CCDC 1552216.†

X-ray diffraction data of **1** and **2** at 110(1) K were collected on an Oxford diffraction “Gemini-R” CCD diffractometer with graphite monochromated  $\text{MoK}_\alpha$  radiation using an Oxford Instrument Cryojet system. Raw data reduction to  $F^2$  was carried out using CrysAlisPro, Oxford Diffraction Ltd. The structures were solved by direct methods and refined by the full-matrix least-squares method against  $F^2$  using SHELX-2013.<sup>17</sup> Non-hydrogen atoms were refined anisotropically. The positions of hydrogen atoms were calculated geometrically. One solvent  $\text{C}_6\text{H}_4\text{Cl}_2$  molecule with the 0.5 occupancy is positioned in both **1** and **2** in the inversion centers and is statistically disordered between two orientations. The positions of hydrogen atoms in the center of  $\text{H}_2\text{TPCor}^{2-}$  in **1** were calculated geometrically. The insertion of three hydrogen atoms in the center of the corrole macrocycle results in very short H...H contacts (less than  $1.4 \text{ \AA}$ ). Therefore, we suppose that only two hydrogen atoms are positioned in the center of the corrole macrocycle in **1**. The third hydrogen atom can be present in the crystal structure of **1** as a counteraction but its exact position could not be unambiguously determined. Therefore, this hydrogen atom was omitted from the cif file. Hydrogen atoms in the center of  $\text{H}_2\text{TPCor}^-$  in **2** are found at two positions near two oppositely located pyrrole nitrogen atoms with the 0.58(2)/0.48(2) occupancies (as shown in Fig. 3b). To keep the anisotropic thermal parameters of the disordered fragments within the reasonable limits, the displacement components were restrained using the ISOR, SIMU and DELU SHELXL instructions. This resulted in 271 and 246 restraints used for the refinement of the crystal structures of **1** and **2**.

### Theoretical calculations

Theoretical calculations were performed using the PBE density functional method<sup>18</sup> and the  $\Lambda_2$  basis<sup>19</sup> of cc-pVTZ quality. Atomic distribution of charge was determined by the Hirschfeld method.<sup>20</sup> All calculations were performed using the PRIRODA program package<sup>21</sup> at the Joint Supercomputer Center of the Russian Academy of Sciences.

## Conclusions

In conclusion, two types of anionic forms of 5,10,15-triphenyl-corroles were obtained and studied in the crystalline state for the first time: diamagnetic deprotonated  $\text{H}_2\text{TPCor}^-$  anions

and paramagnetic deprotonated and reduced  $\text{H}_2\text{TPCor}^{2-}$  dianions. In both cases, deprotonation provides a nearly planar shape of the corrole macrocycle unlike the neutral corrole, which has a non-planar shape due to the strong repulsion of hydrogen atoms.<sup>9</sup> The  $\text{H}_3\text{TPCor}^{\cdot-}$  radical anions cannot be obtained in the solid state due to their instability. Paramagnetic radical  $\text{H}_2\text{TPCor}^{2-}$  dianions are synthetically available when strong reductants like decamethylchromocene are used. Therefore, corroles can also be used in the design of magnetic and probably conducting assemblies in the reduced form. Until now, such assemblies have been developed with phthalocyanines and porphyrins only.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was supported by the Russian Science Foundation grant no. 17-13-01215, JSPS KAKENHI Grant Number JP26288035, and the JST (ACCEL) 27 (100150500010) project.

## Notes and references

- (a) C. G. Claessens, W. J. Blau, M. Cook, M. Hanack, R. J. M. Nolte, T. Torres and D. Wöhrle, *Monatsh. Chem.*, 2001, **132**, 3–11; (b) D. Wöhrle, G. Schnurpfeil, S. G. Makarov, A. Kazarin and O. N. Suvorova, *Macroheterocycles*, 2012, **5**, 191–202.
- (a) J. L. Petersen, C. S. Schramm, D. R. Stojakovic, B. M. Hoffman and T. J. Marks, *J. Am. Chem. Soc.*, 1977, **99**, 286–288; (b) H. Hasegawa, T. Naito, T. Inabe, T. Akutagawa and T. Nakamura, *J. Mater. Chem.*, 1998, **8**, 1567–1570; (c) T. Inabe and H. Tajima, *Chem. Rev.*, 2004, **104**, 5503–5534.
- (a) J. S. Miller, C. Vazquez, J. C. Calabrese, R. S. McLean and A. J. Epstein, *Adv. Mater.*, 1994, **6**, 217–221; (b) W. Hibbs, D. K. Rittenberg, K.-I. Sugiura, B. M. Burkhardt, B. G. Morin, A. M. Arif, L. Liable-Sands, A. L. Rheingold, M. Sundaralingam, A. J. Epstein and J. S. Miller, *Inorg. Chem.*, 2001, **40**, 1915–1925; (c) D. V. Konarev, L. V. Zorina, S. S. Khasanov, E. U. Hakimova and R. N. Lyubovskaya, *New J. Chem.*, 2012, **36**, 48–51; (d) D. V. Konarev, S. S. Khasanov, M. Ishikawa, A. Otsuka, H. Yamochi, G. Saito and R. N. Lyubovskaya, *Dalton Trans.*, 2017, **46**, 3492–3499.
- (a) I. Aviv and Z. Gross, *Chem. Commun.*, 2007, 1987–1999; (b) R. Paolesse, *Synlett*, 2008, **15**, 2215–2230; (c) R. Orłowski, D. Gryko and D. T. Gryko, *Chem. Rev.*, 2017, **117**, 3102–3137.
- J. Shen, J. Shao, Z. Ou, W. E. B. Koszarna, D. T. Gryko and K. M. Kadish, *Inorg. Chem.*, 2006, **45**, 2251–2265.
- J. L. Robbins, N. Edelstein, B. Spencer and J. C. Smart, *J. Am. Chem. Soc.*, 1982, **104**, 1882–1893.



- 7 D. V. Konarev, S. S. Khasanov and R. N. Lyubovskaya, *Asian J. Org. Chem.*, 2017, **6**, 1028–1033.
- 8 B. Koszarna and D. T. Gryko, *J. Org. Chem.*, 2006, **71**, 3707–3717.
- 9 (a) T. Ding, J. D. Harvey and C. J. Ziegler, *J. Porphyrins Phthalocyanines*, 2005, **9**, 22–27; (b) R.-B. Du, C. Liu, D.-M. Shen and Q.-Y. Chen, *Synlett*, 2009, 2701–2705.
- 10 (a) D. V. Konarev, L. V. Zorina, S. S. Khasanov, A. L. Litvinov, A. Otsuka, H. Yamochi, G. Saito and R. N. Lyubovskaya, *Dalton Trans.*, 2013, **42**, 6810–6816; (b) D. V. Konarev, A. V. Kuzmin, M. A. Faraonov, M. Ishikawa, Y. Nakano, S. S. Khasanov, A. Otsuka, H. Yamochi, G. Saito and R. N. Lyubovskaya, *Chem. – Eur. J.*, 2015, **21**, 1014–1028; (c) J. A. Cissell, T. P. Vaid and A. L. Rheingold, *Inorg. Chem.*, 2006, **45**, 2367–2369.
- 11 (a) J. S. Miller, R. S. Mclean, C. Vazquez, J. C. Calabrese, F. Zuo and A. J. Epstein, *J. Mater. Chem.*, 1993, **3**, 215–218; (b) D. V. Konarev, S. S. Khasanov, A. Otsuka and G. Saito, *J. Am. Chem. Soc.*, 2002, **124**, 8520–8521.
- 12 J. Blümel, M. Herker, W. Hiller and F. H. Köhler, *Organometallics*, 1996, **15**, 3474–3476.
- 13 D. V. Konarev, S. S. Khasanov, A. V. Kumin, Y. Nakano, M. Ishikawa, A. Otsuka, H. Yamochi, G. Saito and R. N. Lyubovskaya, *Inorg. Chem.*, 2017, **56**, 1804–1813.
- 14 (a) J. S. Swanson and J. M. Williams, *Inorg. Nucl. Chem. Lett.*, 1970, **6**, 271–276; (b) J. L. Atwood, S. G. Bott, A. W. Coleman, K. D. Robinson, S. B. Whetstone and C. M. Means, *J. Am. Chem. Soc.*, 1987, **109**, 8100–8101.
- 15 D. V. Konarev, S. S. Khasanov, G. Saito, A. Otsuka, Y. Yoshida and R. N. Lyubovskaya, *J. Am. Chem. Soc.*, 2003, **125**, 10074–10083.
- 16 (a) A. Fidalgo-Marijuan, G. Barandika, B. Bazán, M. K. Urtiaga, E. S. Larrea, M. Iglesias, L. Lezamab and M. I. Arriortua, *Dalton Trans.*, 2015, **44**, 213–222; (b) G. Nandia and S. Sarkar, *J. Porphyrins Phthalocyanines*, 2014, **18**, 1–8.
- 17 G. M. Sheldrick, *Acta Crystallogr., Sect. A: Fundam. Crystallogr.*, 2008, **64**, 112–120.
- 18 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.
- 19 D. N. Laikov, *Chem. Phys. Lett.*, 2005, **416**, 116–120.
- 20 F. L. Hirshfeld, *Theor. Chim. Acta*, 1977, **44**, 129–138.
- 21 D. N. Laikov, *Chem. Phys. Lett.*, 1997, **281**, 151–156.

