

Cite this: *RSC Adv.*, 2017, 7, 1464

# The role of Yb<sup>3+</sup> concentrations on Er<sup>3+</sup> doped SrLaMgTaO<sub>6</sub> double perovskite phosphors

Do Rim Kim,<sup>a</sup> Sung Wook Park,<sup>a</sup> Byung Kee Moon,<sup>a</sup> Sung Heum Park,<sup>a</sup> Jung Hyun Jeong,<sup>\*a</sup> Haeyoung Choi<sup>b</sup> and Jung Hwan Kim<sup>\*b</sup>

Er<sup>3+</sup>, Yb<sup>3+</sup> co-doped SrLaMgTaO<sub>6</sub> phosphors have been synthesized by a solid state reaction method. Under a 975 nm excitation, the SrLaMgTaO<sub>6</sub>:Er<sup>3+</sup>/Yb<sup>3+</sup> phosphors exhibited strong green luminescence centered at 525 nm and 545 nm and relatively weak red anti-stokes luminescence centered at 660 nm. Herein, we have established the upconversion mechanism based on the down conversion and upconversion photoluminescence (UCPL) properties. The sensitized energy upconversion [s-ETU2: Yb<sup>3+</sup> (<sup>2</sup>F<sub>5/2</sub>) + Er<sup>3+</sup> (<sup>4</sup>I<sub>11/2</sub>) → Yb<sup>3+</sup> (<sup>2</sup>F<sub>7/2</sub>) + Er<sup>3+</sup> (<sup>4</sup>F<sub>7/2</sub>)] is a main route of green UCPL, and the energy back transfer [EBT: Er<sup>3+</sup> (<sup>4</sup>S<sub>3/2</sub>) + Yb<sup>3+</sup> (<sup>2</sup>F<sub>7/2</sub>) → Er<sup>3+</sup> (<sup>4</sup>I<sub>13/2</sub>) + Yb<sup>3+</sup> (<sup>2</sup>F<sub>5/2</sub>)] is a main route of red UCPL, which reduces the green UCPL to a certain degree. The reduced green and red UCPL of the sample with a high concentration of Yb<sup>3+</sup> is mainly attributed to the concentration quenching of the Yb<sup>3+</sup> ion.

Received 6th October 2016  
Accepted 11th November 2016

DOI: 10.1039/c6ra24808j

www.rsc.org/advances

## 1. Introduction

It is expected that the luminous behavior of lanthanide ions will play a significant role for luminescent materials in specific applications, while the structure of the host matrix imposes great effects on the behavior of the lanthanide phosphors.<sup>1,2</sup> Lanthanide doped upconversion phosphors have received growing attention owing to their wide range of potential applications in many fields, including luminescence display panels, biological imaging, solid-state lasers, solar cells, and temperature sensors.<sup>3–8</sup> Among the lanthanide ions, Er<sup>3+</sup> ion is a promising competitor for UC luminescence centers due to its abundant energy levels with a long lifetime.<sup>9</sup> Moreover, Yb<sup>3+</sup> ion is usually employed as the sensitizer for Er<sup>3+</sup> ion due to its large absorption cross section around 975 nm wavelength and the advantage of an efficient energy transfer process between Yb<sup>3+</sup> and Er<sup>3+</sup> ions. However, host materials are also important for obtaining efficient luminescent properties by the upconversion process. In order to obtain the efficient UC phosphors, it is generally believed that it requires lower phonon energies of the host materials, which leads to minimizing non-radiative losses. Additionally, the upconversion photoluminescence (UCPL) properties depend on many factors of the host materials such as the symmetry, lattice parameters, doping concentration of the activator and sensitizer ions.<sup>10,11</sup> However, the knowledge related to the influence of crystal structure on the UCPL is quite limited.

By virtue of quite interesting structural, electronic as well as magnetic properties of the double perovskite,<sup>12</sup> the AA'BB'O<sub>6</sub> structured phosphors have been well established.<sup>13–15</sup> Since the energy transfer mechanism between donor and acceptor species has been treated within the framework of the Förster and Dexter approaches,<sup>16,17</sup> it is important to know the symmetry site of the donor and acceptor in the phosphors. In a typical double perovskite structure, both B and B' are coordinated by orderly arranged six oxygen atoms. A (or A') site has various coordination numbers from eight to twelve according to the distortion degree of the crystal structure.

In the several mechanisms for the upconversion processes, the main UC processes are ground state absorption followed by excited state absorption (GSA/ESA), energy transfer UC between same kinds of ions (GSA/ETU), and energy transfer UC between activator and sensitizer ion (GSA/s-ETU). The rates of energy transfer (ET) between donor and acceptor are strongly dependent on the crystal structure. In the SrLaMgTaO<sub>6</sub> crystal, two kinds of B ions are ordered and formed a three-dimensional network of alternating MgO<sub>6</sub> and TaO<sub>6</sub> octahedra. Since the tolerance factor (*t*) of complex perovskite SrLaMgTaO<sub>6</sub> are related to the ionic radii of Mg and Ta cations, *t* = 0.952 < 1,<sup>18</sup> both of the MgO<sub>6</sub> and the TaO<sub>6</sub> octahedral tilting distortions exist in this crystal. To the best of our knowledge, there are no reports available on the synthesis and upconversion properties of the SrLaMgTaO<sub>6</sub> except our recent work.<sup>19</sup>

The present paper deals with the influence of Yb<sup>3+</sup> concentration on the luminescence properties in SrLaMgTaO<sub>6</sub> phosphors with fixed Er<sup>3+</sup> concentration to 7 mol% and inducing Yb<sup>3+</sup> concentration from 0% to 10.5 mol%. The crystal structure, optical properties and electronic structure of SrLaMgTaO<sub>6</sub> were investigated experimentally and theoretically. The

<sup>a</sup>Department of Physics, Pukyong National University, Busan 608-737, Republic of Korea. E-mail: jhjeong@pknu.ac.kr

<sup>b</sup>Department of Physics Dongguk University, Busan 614-714, Republic of Korea. E-mail: kimjih@deu.ac.kr; Fax: +82-51-629-5549; Tel: +82-51-629-5564



upconversion luminescence behaviors of the phosphor have been discussed in detail with luminescence mechanisms.

## 2. Experimental and calculation methods

### 2.1 Sample preparation

Crystalline powder samples of  $\text{SrLaMgTaO}_6:\text{Er}^{3+}$  (7%) codoped with  $\text{Yb}^{3+}$  (0%, 3.5%, 7%, 10.5%) were prepared by a solid state reaction method. The  $\text{SrCO}_3$  (99.994%),  $\text{La}_2\text{O}_3$  (99.99%),  $(\text{MgCO}_3)_4\text{Mg}(\text{OH})_2 \cdot 5\text{H}_2\text{O}$  (99.99%),  $\text{Ta}_2\text{O}_5$  (99.99%),  $\text{Er}_2\text{O}_3$  (99.9%) and  $\text{Yb}_2\text{O}_3$  (99.99%) were used as starting materials. All the reagents were purchased from Sigma-Aldrich. The required amounts were weighed according to the stoichiometric ratio and ground to a fine powder using agate mortar and pestle. The mixture of starting materials was preheated at 600 °C for 2 h and then calcined at 900 °C for another 2 h and slowly cooled down naturally to room temperature. Finally, these materials were annealed at 1400 °C at a rate of 5 °C  $\text{min}^{-1}$  and kept for 12 h before cooling down to room temperature.

### 2.2 Characterization and optical measurements

The phase identification of the prepared phosphors was characterized by powder X-ray diffraction (XRD) analysis on a Philips X'Pert MPD diffractometer (Philips, Netherlands) using  $\text{CuK}\alpha$  radiation ( $\lambda = 1.546 \text{ \AA}$ ). The UCPL emission spectra were recorded with a fluorescence spectrophotometer (Acton SpectraPro 750-Triplet Grating Monochromator) from CCD detector (Princeton EEV 10241024 and PI-Max 133 Controller). All the measurements except photoluminescence (PL) spectra of  $\text{SrLaMgTaO}_6$  were performed at room temperature. The sample was placed in a liquid helium flow cryostat for the measurements of PL spectra of  $\text{SrLaMgTaO}_6$  at 20–300 K.

## 3. Results and discussion

### 3.1 XRD patterns and crystal structure

The ionic radii of  $\text{Er}^{3+}$  ( $R = 1.01 \text{ \AA}$ , CN = 12) and  $\text{Yb}^{3+}$  ( $R = 1.01 \text{ \AA}$ , CN = 12) are slightly smaller than  $\text{Sr}^{2+}$  ( $R = 1.18 \text{ \AA}$ , CN = 12) and  $\text{La}^{3+}$  ( $R = 1.17 \text{ \AA}$ , CN = 12). Therefore,  $\text{Er}^{3+}/\text{Yb}^{3+}$  can be easily substituted into the  $\text{Sr}^{2+}$  and  $\text{La}^{3+}$  site, while the  $\text{Mg}^{2+}$  (0.72 Å, CN = 6) and  $\text{Ta}^{5+}$  (0.64 Å, CN = 6) sites are too small to occupy  $\text{Er}^{3+}/\text{Yb}^{3+}$  ions. The dopant ions were expected to occupy the site of  $\text{La}^{3+}$  ion due to its similar oxidation state and larger ionic radius in the  $\text{SrLaMgTaO}_6:\text{Er}^{3+}/\text{Yb}^{3+}$ , thus, the nominal formula of phosphors is written as  $\text{SrLa}_{(1-x-y)}\text{MgTaO}_6:\text{Er}^{3+}_x\text{Yb}^{3+}_y$ . The structure of synthesized samples was examined by the measuring the XRD patterns, and all the samples exhibited monoclinic structure with space group  $P2_1/n$  (Fig. 1). Within the synthesized dopant limits, all the diffraction peaks are well matched with those in the standard card NIMS (National Institute for Materials Science) without any other characteristic peaks related to raw materials or impurities.

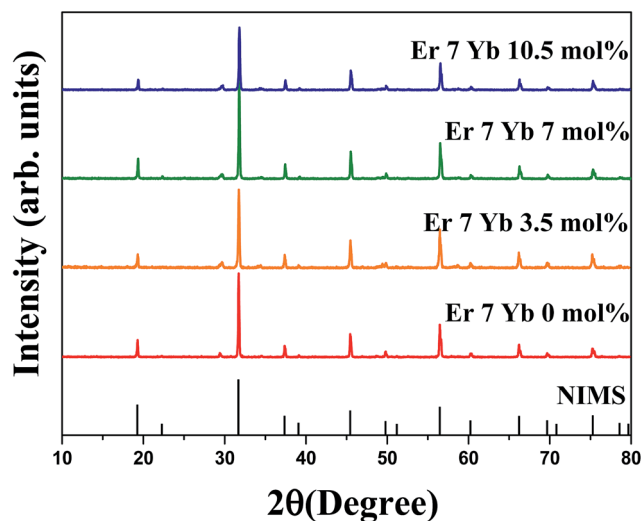


Fig. 1 X-ray diffraction patterns of  $\text{SrLa}_{(0.93-x)}\text{MgTaO}_6:\text{Er}^{3+}/x\text{Yb}^{3+}$  phosphors with a fixed  $\text{Er}^{3+}$  ions (7 mol%) and different concentrations of  $\text{Yb}^{3+}$  ions with the reference data of NIMS.

### 3.2 Photoluminescence (PL) of $\text{SrLaMgTaO}_6$

The sample of  $\text{SrLaMgTaO}_6$  was placed in a liquid helium flow cryostat for the measurements of PL spectra at 20–300 K. Fig. 2 shows the PL spectra of  $\text{SrLaMgTaO}_6$  under an excitation wavelength of 355 nm. The broad and strong emission bands centered at 691 nm and 704 nm were observed at low temperature, which might be attributed to the existence of  $\text{TaO}_6$  emission from  $\text{SrLaMgTaO}_6$  host crystal. As increasing of the sample temperature, the total PL intensity was slightly reduced, and the PL intensity of the band centered 691 nm was highly reduced compared to that of the band centered 704 nm. To our knowledge, the strong red emission at room temperature has not been reported on tantalum based host lattices so far. However, the  $\text{TaO}_6$  emission from  $\text{SrLaMgTaO}_6$  host lattice was observed for the first time. It has been reported that perovskite-

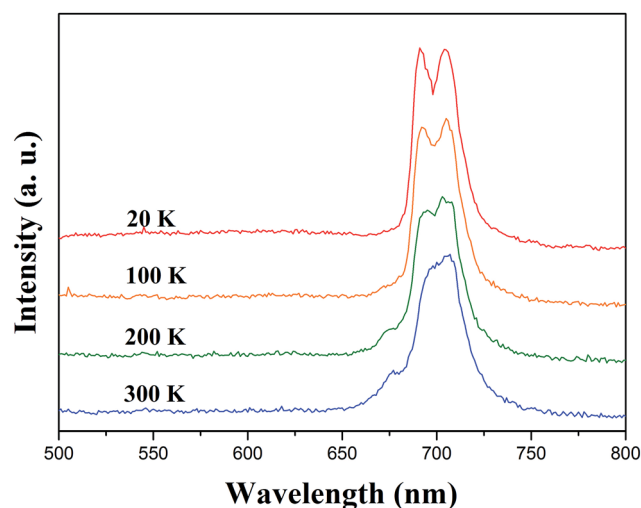


Fig. 2 Photoluminescence spectra of  $\text{SrLaMgTaO}_6$  at different temperature under an excitation wavelength of 355 nm.




**Table 1** Luminescence data of perovskite-like tantalate and molybdate powders

Compound	Emission max (nm)	Excitation max (nm)	Stokes shift ( $10^3 \text{ cm}^{-1}$ )	Temperature (K)	Ref.
KTaO <sub>3</sub>	490	320	10.9	12	20
NaTaO <sub>3</sub>	460	304	11.1	77	21
LiTaO <sub>3</sub>	340	235	14.0	4.2	22
La <sub>2</sub> MoO <sub>6</sub>	675	330	15.7	4.2	23
Sr <sub>2</sub> CaMoO <sub>6</sub>	625	385	9.9	4.2	23
SrLaMgTaO <sub>6</sub>	704	348	14.5	Room temp.	This work

like tantalate powders have an intrinsic emission from TaO<sub>6</sub> group ranging from 340 nm to 490 nm at low temperature, and the emission is quenched by improving temperature. Some reports about PL emitted from Ta–O bond and Mo–O bond are listed in Table 1.

### 3.3 Upconversion photoluminescence of Er<sup>3+</sup> in SrLaMgTaO<sub>6</sub>

The UCPL spectra of SrLaMgTaO<sub>6</sub>:xEr<sup>3+</sup> with different concentration of Er<sup>3+</sup> ions under a 975 nm excitation are shown in Fig. 3. Since the UCPL properties depend on the concentrations of the dopant ions of the activator, it is important to know the relative UCPL intensity emitted by a single Er<sup>3+</sup> ion as function of Er<sup>3+</sup> concentration. In order to compare the green intensities of SrLa<sub>(1-x)</sub>MgTaO<sub>6</sub>:xEr<sup>3+</sup> ( $x = 0.01, 0.03, 0.05, 0.07, 0.1, 0.12$ ), same experimental condition was maintained. The PL intensity per mol is the intensity of green UCL emitted from  $x$  mol% sample divided by  $x$ . We obtained the value for 5 times, and the average values were displayed in inset of Fig. 2. Since the values nearly remained constant up to 7 mol% and then decreased rapidly above 10 mol% of Er<sup>3+</sup> concentration, we fixed the Er<sup>3+</sup> concentration to 7 mol%. The decrement may be attributed to the concentration quenching effect.

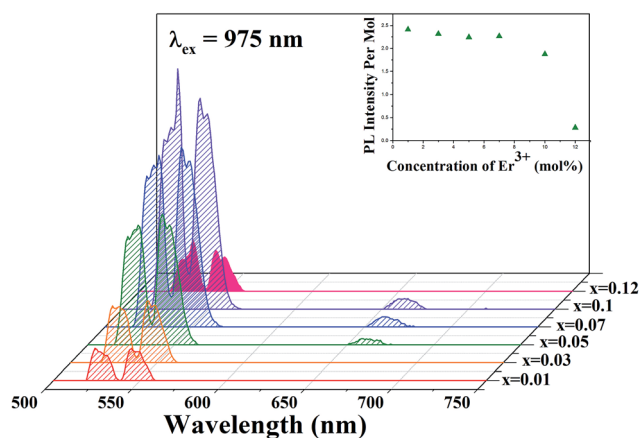


**Fig. 3** The UCPL spectra of SrLaMgTaO<sub>6</sub>:xEr<sup>3+</sup> with different concentration of Er<sup>3+</sup> under a 975 nm excitation. The inset shows the UCPL intensity variation per mol as function of Er<sup>3+</sup> concentration.

### 3.4 Photoluminescence of SrLaMgTaO<sub>6</sub>:Er<sup>3+</sup>/Yb<sup>3+</sup>

Fig. 4(a) shows the photoluminescence (PL) spectra of SrLaMgTaO<sub>6</sub>:Er<sup>3+</sup>/Yb<sup>3+</sup> under an excitation wavelength of 355 nm. Two typical green emission bands centered at 525 and 545 nm are assigned to the <sup>2</sup>H<sub>11/2</sub> → <sup>4</sup>I<sub>15/2</sub>, and <sup>4</sup>S<sub>3/2</sub> → <sup>4</sup>I<sub>15/2</sub> transitions, respectively. A relatively weak red emission band centered at 660 nm assigned to <sup>4</sup>F<sub>9/2</sub> → <sup>4</sup>I<sub>15/2</sub> transition. The strong emission band centered at 704 nm from Er<sup>3+</sup> single doped SrLaMgTaO<sub>6</sub> host crystal was observed, which was due to the TaO<sub>6</sub> emission. By incorporation of Yb<sup>3+</sup> ion, dramatically weakened PL seems to be due to the energy transfer from the TaO<sub>6</sub> band to <sup>2</sup>F<sub>7/2</sub> state of Yb<sup>3+</sup> which has high absorption cross-section.

Fig. 4(b) shows the PLE spectra of SrLaMgTaO<sub>6</sub>:Er<sup>3+</sup>/Yb<sup>3+</sup> monitored at 704 nm host emission. The wide band centered at 348 nm seems to be emitted from exciton of the crystal related to Ta–O charge transfer band. The excitation energy of SrLaMgTaO<sub>6</sub> is lower than those of other tantalate as can be seen in Table 1. It is well known that the energy of charge transfer transition from ligand to central metal ion is dependent on the coordination number.<sup>24</sup> The orbital mixing of Ta<sup>5+</sup> and O<sup>2-</sup> of TaO<sub>6</sub> octahedron is larger than that of TaO<sub>4</sub>

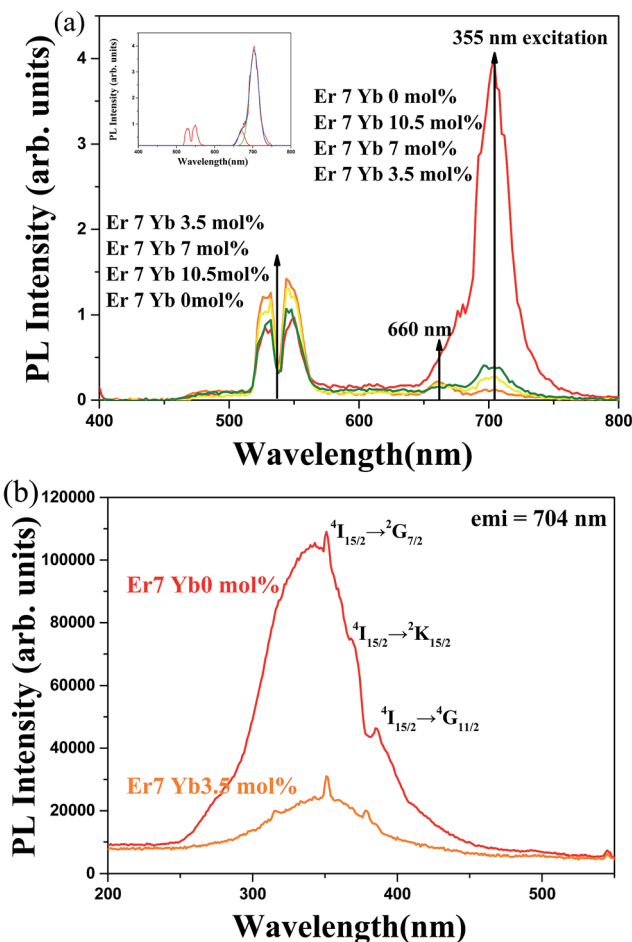

**Fig. 4** The excitation and emission spectra of SrLaMgTaO<sub>6</sub>:Er<sup>3+</sup>/Yb<sup>3+</sup> phosphor with different concentration of Yb<sup>3+</sup>: (a) DCPL spectra under a 355 nm excitation, (b) PLE spectra monitored at 704 nm.



tetrahedron. Since the required energy decreases to transfer an electron from  $O^{2-}$  to  $Ta^{5+}$  ion, the CT band will move to lower energy region. And three sharp peaks at 351 nm, 368 nm and 385 nm comes from  $^4I_{15/2} \rightarrow ^2G_{7/2}$ ,  $^4I_{15/2} \rightarrow ^2K_{15/2}$ , and  $^4I_{15/2} \rightarrow ^4G_{11/2}$  of the  $Er^{3+}$  ion, respectively. The Stokes shift of the  $SrLaMgTaO_6$  crystal is  $14\,500\text{ cm}^{-1}$ , which is slightly higher than those of other perovskite-like tantalate. Since the bonding structure of Ta–O in the imperfection crystal is complicated, further specialized research should be performed to obtain exact bonding structure.

### 3.5 Upconversion photoluminescence of $Er^{3+}/Yb^{3+}$ in $SrLaMgTaO_6$

Fig. 5 shows the UCPL spectra of  $SrLaMgTaO_6:Er^{3+}/Yb^{3+}$  under an excitation wavelength of 975 nm. Two typical green UCPL bands and a relatively weak red UCPL band are observed, which are similar to those of down conversion luminescence (DCPL) bands shown in Fig. 4(a). However, the intensity of green DCPL is nearly independent on the concentration of  $Yb^{3+}$ , the overall UCPL intensities are greatly enhanced with introducing sensitizer  $Yb^{3+}$  ion owing to the efficient energy transfer from  $Yb^{3+}$  to  $Er^{3+}$ , which is also known as sensitized energy transfer upconversion (s-ETU). The intensity of UCPL has been continuously enhanced with increasing the  $Yb^{3+}$  ion and reaches a maximum value at a concentration of 7 mol%. As the concentration of  $Yb^{3+}$  has further increased, the UCPL intensity had reduced. Both of the concentration quenching rate among  $Yb^{3+}$  ions and the rate of the energy back transfer (EBT) from  $Er^{3+}$  to  $Yb^{3+}$  [ $Er^{3+} (^4S_{3/2}) + Yb^{3+} (^2F_{7/2}) \rightarrow Er^{3+} (^4I_{13/2}) + Yb^{3+} (^2F_{5/2})$ ] become active with further doping of  $Yb^{3+}$ , which seems to be the main reasons of the reducing UCPL intensity.

Fig. 6 shows the temporal behaviours of the green emission of the  $^4S_{3/2}$  level under a 355 nm excitation with pulse duration of 6 ns. The decay times of the  $^4S_{3/2}$  level become shorter from

122 to 92  $\mu s$  as the  $Yb^{3+}$  concentrations increases from 0 to 10.5 mol%. It is attributed to the energy transfer from  $^4S_{3/2}$  state of  $Er^{3+}$  to  $Yb^{3+}$  ion. Since  $Yb^{3+}$  ion has only two levels, the energy transfer from  $Er^{3+}$  to  $Yb^{3+}$ , so called EBT [EBT:  $Er^{3+} (^4S_{3/2}) + Yb^{3+} (^2F_{7/2}) \rightarrow Er^{3+} (^4I_{13/2}) + Yb^{3+} (^2F_{5/2})$ ] can be possible. The efficiency of EBT defined as the ratio of EBT rate to total emission rate of  $^4S_{3/2}$  state was calculated by the following equation:  $\eta = \frac{1/\tau(x) - 1/\tau(0)}{1/\tau(x)} = \frac{\tau(x) - \tau(0)}{\tau(0)}$ , where,  $\tau(x)$  is the decay time of the  $^4S_{3/2}$  level in  $SrLaMgTaO_6$  with  $x$  mol% concentration of  $Yb^{3+}$  and 7 mol% of  $Er^{3+}$ . The efficiency of EBT that has calculated from decay times is displayed in Fig. 7(a). Since the EBT plays a role to reduce the green UCL intensity, it is important to know EBT efficiency. It has increased linearly from 0 to 24% as the  $Yb^{3+}$  concentration increases from 0 to 10.5 mol%.

If the UCPL green emission is only due to the ESA process, the decay times of the  $^4S_{3/2}$  under a 975 nm excitation will be similar with that of 355 nm excitation. However, by incorporation of sensitizer such as  $Yb^{3+}$ , the sensitized energy transfer upconversion (s-ETU) process that has additionally participated in the UCPL process makes the decay curves delayed. Two different variations of the decay time as function of the  $Yb^{3+}$  concentration are shown in Fig. 7(b). The pulsed light of a 975 nm was generated from the optical parametric oscillator pumped from the 3<sup>rd</sup> harmonics of Nd:YAG laser with pulse duration of 6 ns. Small differences of decay time between UCPL and DCPL at  $x = 0$  is attributed to the ETU process which is more active in the highly  $Er^{3+}$  dopant sample. The concentration of  $Er^{3+}$  of all samples is fixed to 7.0 mol%. By addition of sensitizer  $Yb^{3+}$  ion, the DCPL decay times has reduced due to the EBT, however, the UCPL decay times had increased due to the s-ETU from  $Yb^{3+}$  to  $Er^{3+}$ . As seen in Fig. 5, increase of the UCPL intensities up to 7 mol% of  $Yb^{3+}$  concentration are attributed to the enhanced s-ETU. At highly dopant sample, the excited state of  $Yb^{3+}$  ( $^2F_{5/2}$ ) will be quenched by the highly enhanced energy migration among  $Yb^{3+}$ , which makes the

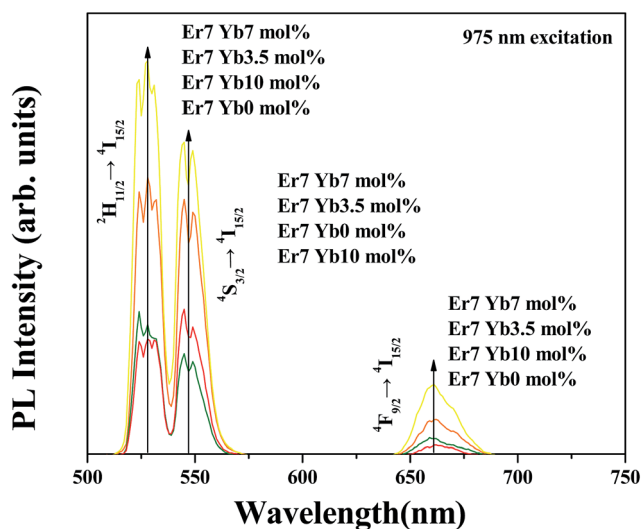


Fig. 5 Upconversion photoluminescence spectra of  $SrLaMgTaO_6:Er^{3+}/Yb^{3+}$  phosphors with different concentration of  $Yb^{3+}$ : UCPL spectra under a 975 nm excitation.

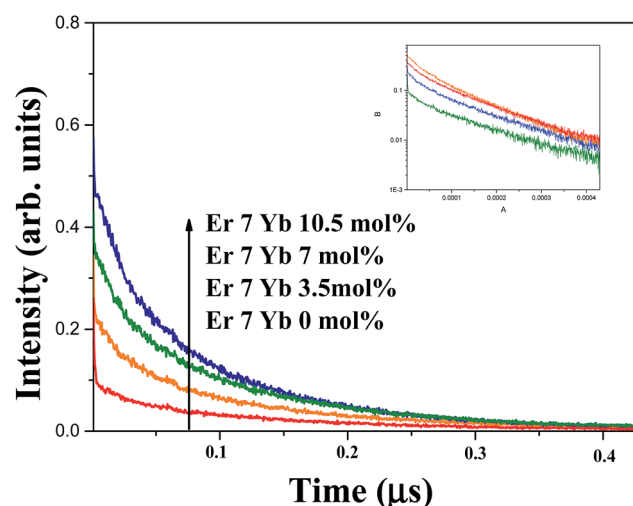


Fig. 6 Decay curves of  $SrLaMgTaO_6:Er^{3+}/Yb^{3+}$  phosphor monitored at 545 nm under (a) 355 nm excitation and (b) 975 nm excitation.





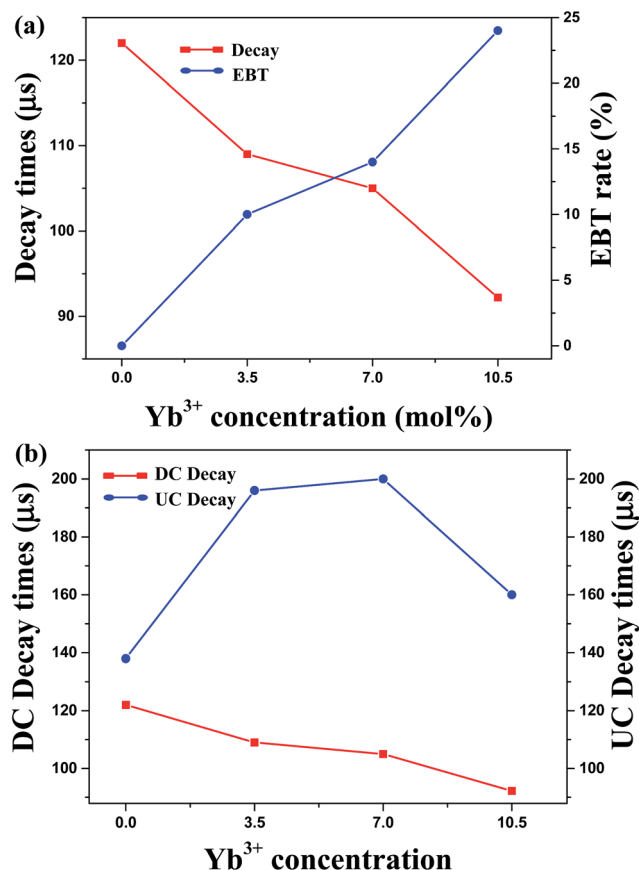


Fig. 7 (a) Decay time of the  $^4S_{3/2}$  and EBT rate from  $Er^{3+}$  to  $Yb^{3+}$  ions in  $SrLaMgTaO_6$  phosphors with different concentration of  $Yb^{3+}$  ion. (b) The decay time of downconversion and upconversion as function of the  $Yb^{3+}$  concentration.

reduction of s-ETU rate. The rate of s-ETU which is dependent on the concentration of sensitizer is limited by the concentration quenching of sensitizer. In short, lower value of the UCPL decay time at  $x = 10.5$  sample are resulted from the concentration quenching of  $Yb^{3+}$  and the EBT from  $Er^{3+}$  to  $Yb^{3+}$ .

The possible populating process of the  $Er^{3+}$  and  $Yb^{3+}$  for the UCPL under the excitation of 975 nm are shown in Fig. 8. By absorbing NIR photons, GSA of  $Yb^{3+}$  ion and  $Er^{3+}$  ion takes place as following:  $^2F_{7/2} + \text{a photon (975 nm)} \rightarrow ^2F_{5/2}$  in  $Yb^{3+}$  and  $^4I_{15/2} + \text{a photon (975 nm)} \rightarrow ^4I_{11/2}$  in  $Er^{3+}$ . Most of incident energy is absorbed by the  $Yb^{3+}$  ions due to the larger absorption cross section around 975 nm wavelength comparing to that of  $Er^{3+}$ . Therefore, the population at excited level  $^4I_{11/2}$  mainly occurs through energy transfer from  $Yb^{3+}$  to  $Er^{3+}$  [s-ET:  $Yb^{3+} (^2F_{5/2}) + Er^{3+} (^4I_{15/2}) \rightarrow Yb^{3+} (^2F_{7/2}) + Er^{3+} (^4I_{11/2})$ ]. The two UCPL green emission bands around 525 and 545 nm are radiated from  $^2H_{11/2}$  and  $^4S_{3/2} \rightarrow ^4I_{15/2}$  transitions, respectively. The green emission levels  $^2H_{11/2}$  and  $^4S_{3/2}$  are populated by multiphonon relaxation from upper level  $^4F_{7/2}$ . The excited state of  $^4F_{7/2}$  could be populated through the s-ETU2 process [s-ETU2:  $Yb^{3+} (^2F_{5/2}) + Er^{3+} (^4I_{11/2}) \rightarrow Yb^{3+} (^2F_{7/2}) + Er^{3+} (^4F_{7/2})$ ] or excited state absorption [ESA1:  $Er^{3+} (^4I_{11/2}) + \text{a photon (975 nm)} \rightarrow Er^{3+} (^4F_{7/2})$ ]. The UCPL red emitting state  $^4F_{9/2}$  can be populated

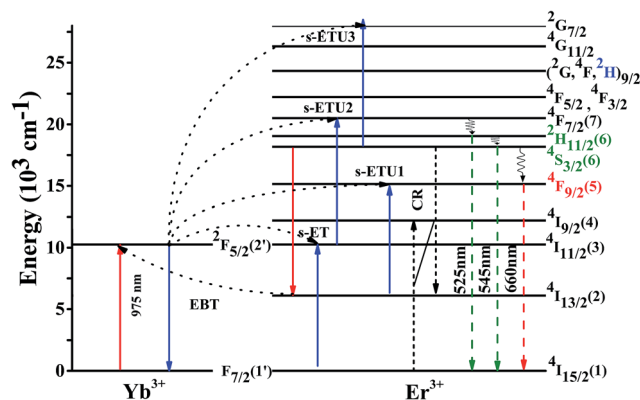


Fig. 8 The schematic energy level diagrams of  $Er^{3+}$  and  $Yb^{3+}$  ions in the  $SrLaMgTaO_6:Er^{3+}/Yb^{3+}$  and the possible mechanisms of the upconversion.

through three possible processes. The first is multiphonon relaxation from the  $^4S_{3/2}$  level to  $^4F_{9/2}$ . The second is due to generation of the  $^4I_{13/2}$  state that can be populated through the cross relaxation process [CR:  $Er^{3+} (^4I_{15/2}) + Er^{3+} (^4S_{3/2}) \rightarrow Er^{3+} (^4I_{9/2}) + Er^{3+} (^4I_{13/2})$ ]. The red  $^4F_{9/2}$  state is populated from  $^4I_{13/2}$  state through the s-ETU1 process [ $Yb^{3+} (^2F_{5/2}) + Er^{3+} (^4I_{13/2}) \rightarrow Yb^{3+} (^2F_{7/2}) + Er^{3+} (^4F_{9/2})$ ] or ESA2 process [ $^4I_{13/2} + \text{a photon (975 nm)} \rightarrow Er^{3+} (^4F_{9/2})$ ]. Another possible mechanism to populate  $^4I_{13/2}$  level is an EBT process [EBT:  $Er^{3+} (^4S_{3/2}) + Yb^{3+} (^2F_{7/2}) \rightarrow Er^{3+} (^4I_{13/2}) + Yb^{3+} (^2F_{5/2})$ ]. As can be seen in Fig. 5, the red UCPL intensity of the sample doped with 7 mol%  $Er^{3+}$  is very smaller than that of co-doped with 7 mol%  $Er^{3+}$  and 7 mol%  $Yb^{3+}$ . Considering the multiphonon relaxation and the CR processes are independent of the concentration of  $Yb^{3+}$  ion, the UCPL red emission is mainly attributed to the EBT process. As increasing  $Yb^{3+}$  concentration, the enhanced rate of EBT results in higher red UCPL emission. As further doping of  $Yb^{3+}$  up to 7 mol%, the population of  $^2F_{5/2}$  state that is an initial state of s-ETU2 process will be quickly reduced owing to the concentration quenching of  $Yb^{3+}$ . Since the initial state of EBT,  $Er^{3+} (^4S_{3/2})$ , is easily populated via a multiphonon relaxation from the final state of s-ETU2,  $Er^{3+} (^4F_{7/2})$ , the reduction of s-ETU2 process is followed by reduction of EBT. Consequently, the reduced green and red UCPL of the sample with 10.5 mol%  $Yb^{3+}$  is chiefly attributed to the concentration quenching of  $Yb^{3+}$ .

The logarithmic scale dependence of the UC emission intensities of  $^4S_{3/2} \rightarrow ^4I_{15/2}$  (green) transition on the working pump power over the range of 100 to 1000 W in the  $SrLaMgTaO_6:Er^{3+}/Yb^{3+}$  phosphor is shown in Fig. 9. The number of photons required to populate the upper level under unsaturated condition can be described by relation:  $I_{up} = (P_{pump})^n$ . Where  $I_{up}$  is the UCPL emission intensity,  $P_{pump}$  is the power of the pump laser and  $n$  is the number of pumped photons required in the mechanism which is indicated by the slope. The value of  $n$  obtained in  $SrLaMgTaO_6:Er^{3+}/Yb^{3+}$  phosphors with the monoclinic structure were 1.56 for green UCL. The slope value of  $^4S_{3/2}$  level of  $Er^{3+}$  indicate that the two photon processes are mainly responsible for green emission.



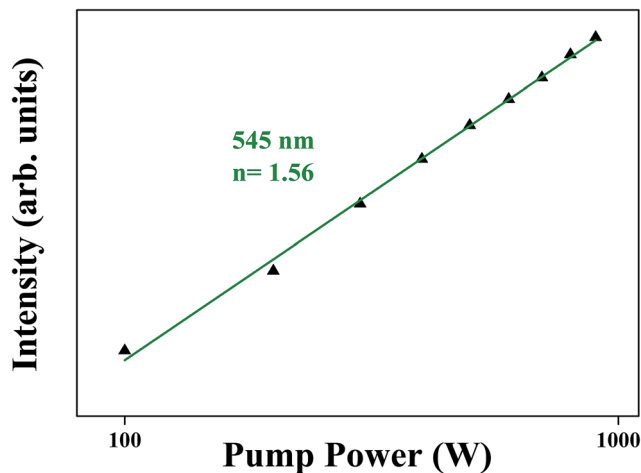


Fig. 9 The Pump power dependence of the green emission intensity, slope = 1.56.

## 4. Conclusions

SrLaMgTaO<sub>6</sub>:0.07Er<sup>3+</sup>/xYb<sup>3+</sup> ( $x = 0, 0.035, 0.07, 0.105$ ) phosphors were prepared by a solid reaction method. Under a 355 nm excitation, strong red PL was observed at room temperature, which seems to be emitted from Ta–O bond in SrLaMgTaO<sub>6</sub> powder. Under 975 nm laser diode excitation, both UCPL green and red emissions are enhanced by incorporation of Yb<sup>3+</sup>. As the concentration of Yb<sup>3+</sup> increases, s-ETU [s-ETU2: Yb<sup>3+</sup> (<sup>2</sup>F<sub>5/2</sub>) + Er<sup>3+</sup> (<sup>4</sup>I<sub>11/2</sub>) → Yb<sup>3+</sup> (<sup>2</sup>F<sub>7/2</sub>) + Er<sup>3+</sup> (<sup>4</sup>F<sub>7/2</sub>)] process and EBT from Er<sup>3+</sup> to Yb<sup>3+</sup> [EBT: Er<sup>3+</sup> (<sup>4</sup>S<sub>3/2</sub>) + Yb<sup>3+</sup> (<sup>2</sup>F<sub>7/2</sub>) → Er<sup>3+</sup> (<sup>4</sup>I<sub>13/2</sub>) + Yb<sup>3+</sup> (<sup>2</sup>F<sub>5/2</sub>)] become more active. The s-ETU2 is a main route of green UCPL, and the EBT process is a main route of red UCPL and can reduce the green UCPL to a certain degree. As further doping of Yb<sup>3+</sup> up to 7 mol%, the population of <sup>2</sup>F<sub>5/2</sub> state that is an initial state of s-ETU2 process was quickly reduced owing to the concentration quenching of Yb<sup>3+</sup>. Consequently, the reduced green and red UCPL of the sample at 10.5 mol% of Yb<sup>3+</sup> is chiefly attributed to the concentration quenching of Yb<sup>3+</sup>.

## Acknowledgements

This research was supported by the Basic Science Research Program through the National Research Foundation of Korea (NRF) funded by the Ministry of Science, ICT and Future Planning (No. 2015060315). The Er<sup>3+</sup> doped SrLaMgTaO<sub>6</sub> phosphors are supplied by the Display and Lighting Phosphor Bank at Pukyong National University.

## References

- 1 B. Zhou, B. Shi, D. Jin and X. Liu, Controlling upconversion nanocrystals for emerging applications, *Nat. Nanotechnol.*, 2015, **10**, 924–936, DOI: 10.1038/nnano.2015.251.
- 2 J.-M. Li, X.-L. Zeng, Y.-H. Dong and Z.-A. Xu, White-light emission and weak antiferromagnetism from cubic rare-

- earth oxide Eu<sub>2</sub>O<sub>3</sub> electrospun nanostructures, *CrystEngComm*, 2013, 2372–2377, DOI: 10.1039/c3ce26770a.
- 3 Q. Zuo, L. Luo and Y. Yao, The electrical, upconversion emission, and temperature sensing properties of Er<sup>3+</sup>/Yb<sup>3+</sup>-codoped Ba(Zr<sub>0.2</sub>Ti<sub>0.8</sub>)O<sub>3</sub>-(Ba<sub>0.7</sub>Ca<sub>0.3</sub>)TiO<sub>3</sub> ferroelectric ceramics, *J. Alloys Compd.*, 2015, **632**, 711–716, DOI: 10.1016/j.jallcom.2015.01.296.
- 4 F. Huang, Y. Gao, J. Zhou, J. Xu and Y. Wang, Yb<sup>3+</sup>/Er<sup>3+</sup> co-doped CaMoO<sub>4</sub>: a promising green upconversion phosphor for optical temperature sensing, *J. Alloys Compd.*, 2015, **639**, 325–329, DOI: 10.1016/j.jallcom.2015.02.228.
- 5 L. Pihlgren, T. Laihin, L. C. V. Rodrigues, S. Carlson, K. O. Eskola, A. Kotlov, M. Lastusaari, T. Soukka, H. F. Brito and J. Hölsä, On the mechanism of persistent up-conversion luminescence in the ZrO<sub>2</sub>:Yb<sup>3+</sup>,Er<sup>3+</sup> nanomaterials, *Opt. Mater.*, 2014, **36**, 1698–1704, DOI: 10.1016/j.optmat.2014.01.027.
- 6 F. Auzel, Upconversion and Anti-Stokes Processes with f and d Ions in Solids, *Chem. Rev.*, 2004, **104**, 139–173, DOI: 10.1021/cr020357g.
- 7 V. K. Rai, Temperature sensors and optical sensors, *Appl. Phys. B: Lasers Opt.*, 2007, **88**, 297–303, DOI: 10.1007/s00340-007-2717-4.
- 8 J. Hölsä, Persistent Luminescence Beats the Afterglow: 400 Years of Persistent Luminescence, *Electrochem. Soc. Interface*, 2009, **4**, 42–45, [http://www.electrochem.org/dl/interface/wtr/wtr09/wtr09\\_p042-045.pdf](http://www.electrochem.org/dl/interface/wtr/wtr09/wtr09_p042-045.pdf).
- 9 C. Mi, J. Wu, Y. Yang, B. Han and J. Wei, Efficient upconversion luminescence from Ba<sub>5</sub>Gd<sub>8</sub>Zn<sub>4</sub>O<sub>21</sub>:Yb<sup>3+</sup>, Er<sup>3+</sup> based on a demonstrated cross-relaxation process, *Sci. Rep.*, 2016, **6**, 22545, DOI: 10.1038/srep22545.
- 10 B. Chen, B. Dong, J. Wang, S. Zhang, L. Xu, W. Yu and H. Song, Amphiphilic silane modified NaYF<sub>4</sub>:Yb,Er loaded with Eu(TTA)<sub>3</sub>(TPPO)<sub>2</sub> nanoparticles and their multi-functions: dual mode temperature sensing and cell imaging, *Nanoscale*, 2013, **5**, 8541–8549, DOI: 10.1039/c3nr02670a.
- 11 S. Song, Y. Kuang, J. Liu, Q. Yang, L. Luo and X. Sun, Separation and phase transition investigation of Yb<sup>3+</sup>/Er<sup>3+</sup> co-doped NaYF<sub>4</sub> nanoparticles, *Dalton Trans.*, 2013, **42**, 13315–13318, DOI: 10.1039/c3dt51652k.
- 12 K. Goodenough, J. B. Longo and J. M. Hellwege, *Crystallographic and Magnetic Properties of Perovskite and Perovskite-Related Compounds, New Series*, Springer-Verlag, Berlin, 1970.
- 13 M. T. Anderson, K. B. Greenwood, G. A. Taylor and K. R. Poeppelmeier, B-cation arrangements in double perovskites, *Prog. Solid State Chem.*, 1993, **22**, 197–233, DOI: 10.1016/0079-6786(93)90004-B.
- 14 W. T. Fu, Y. S. Au, S. Akerboom and D. J. W. IJdo, Crystal structures and chemistry of double perovskites Ba<sub>2</sub>M(II)M'(VI)O<sub>6</sub> (M = Ca, Sr, M' = Te, W, U), *J. Solid State Chem.*, 2008, **181**, 2523–2529, DOI: 10.1016/j.jssc.2008.06.024.
- 15 S. Ye, Y. Li, D. Yu, Z. Yang and Q. Zhang, Structural effects on Stokes and anti-Stokes luminescence of double-perovskite (Ba,Sr)<sub>2</sub>CaMoO<sub>6</sub>: Yb<sub>3</sub>,Eu<sub>3</sub>, *J. Appl. Phys.*, 2011, **110**, 013517, DOI: 10.1063/1.3602991.



- 16 D. L. Dexter, A Theory of Sensitized Luminescence in Solids, *J. Chem. Phys.*, 1953, **21**, 836, DOI: 10.1063/1.1699044.
- 17 T. Förster, Experimentelle und theoretische Untersuchung des zwischengmolekularen Übergangs von elektronenanregungsenergie, *Naturforscher*, 1949, **4a**, 321–327, DOI: 10.1515/zna-1949-0501.
- 18 Y. Guo, B. Kee Moon, S. Heum Park, J. Hyun Jeong, J. Hwan Kim, K. Jang and R. Yu, A red-emitting perovskite-type  $\text{SrLa}(1-x)\text{MgTaO}_6:x\text{Eu}^{3+}$  for white LED application, *J. Lumin.*, 2015, **167**, 381–385, DOI: 10.1016/j.jlumin.2015.06.054.
- 19 D. R. Kim, S. W. Park, J. H. Jeong, H. Choi and J. H. Kim, Upconversion luminescence properties of  $\text{Er}^{3+}$  in  $\text{SrLaMgTaO}_6$  double perovskite phosphor, *Mater. Res. Bull.*, 2017, **85**, 216–221, DOI: 10.1016/j.materresbull.2016.09.017.
- 20 V. Trepakov, A. Skvortsov, N. Poletaev, Z. Potůček, D. Nuzhnyy, L. Jastrabik and A. Dejneka, An optical and dielectric spectroscopy study of  $\text{Er}^{3+}$ -doped  $\text{KTaO}_3$ , *Phys. Status Solidi*, 2011, **248**, 2908–2915, DOI: 10.1002/pssb.201147080.
- 21 C. C. Hu, C. C. Tsai and H. Teng, Structure characterization and tuning of perovskite-like  $\text{NaTaO}_3$  for applications in photoluminescence and photocatalysis, *J. Am. Ceram. Soc.*, 2009, **92**, 460–466, DOI: 10.1111/j.1551-2916.2008.02869.x.
- 22 M. Wiegel, M. H. J. Emond, E. R. Stobbe and G. Blasse, Luminescence of alkali tantalates and niobates, *J. Phys. Chem. Solids*, 1994, **55**, 773–778, DOI: 10.1016/0022-3697(94)90030-2.
- 23 M. Wiegel and G. Blasse, The luminescence properties of octahedral and tetrahedral molybdate complexes, *J. Solid State Chem.*, 1992, **99**, 388–394, DOI: 10.1016/0022-4596(92)90327-R.
- 24 Y. Li and X. Liu, Sol-gel synthesis, structure and luminescence properties of  $\text{Ba}_2\text{ZnMoO}_6:\text{Eu}^{3+}$  phosphors, *Mater. Res. Bull.*, 2015, **64**, 88–92, DOI: 10.1016/j.materresbull.2014.12.041.

