



CrossMark  
click for updates

Cite this: *RSC Adv.*, 2017, 7, 2676

## Ultraviolet upconversion emission of Pb<sup>2+</sup> ions sensitized by Yb<sup>3+</sup>-trimers in CaF<sub>2</sub>

Tuerxun Aidilibike,<sup>ab</sup> Junjie Guo,<sup>a</sup> Lili Wang,<sup>a</sup> Xiaohui Liu,<sup>a</sup> Yangyang Li<sup>a</sup> and Weiping Qin<sup>\*a</sup>

Under 978 nm near infrared (NIR) excitation, ultraviolet (UV) upconversion (UC) emissions from Pb<sup>2+</sup> ions in CaF<sub>2</sub>:Pb<sup>2+</sup>,Yb<sup>3+</sup> were first observed at room temperature. The UC emission centered at ~383 nm was ascribed to the <sup>3</sup>P<sub>0</sub> → <sup>1</sup>A<sub>1g</sub> (<sup>1</sup>S<sub>0</sub>) transition of Pb<sup>2+</sup> ions. From transient measurements, the UC process was found to be dominated by the energy transfer process: three excited Yb<sup>3+</sup> ions simultaneously transfer their energy to one Pb<sup>2+</sup> ion. With the increase in Pb<sup>2+</sup> concentration, the cooperative luminescence from 3-Yb<sup>3+</sup> clusters decreased gradually until it was extinguished. The cooperative sensitization to one Pb<sup>2+</sup> ion comes from three excited Yb<sup>3+</sup> ions, which is a four-ion process and exhibits a third power dependence on the NIR pumping power.

Received 17th October 2016  
Accepted 9th December 2016

DOI: 10.1039/c6ra25344j

[www.rsc.org/advances](http://www.rsc.org/advances)

Optical frequency UC is a luminescence technology developed since the 1960s. Thanks to the successful fabrications of powerful infrared (IR) diode lasers and heavy metal fluoride glasses, visible (VIS) upconversion luminescence (UCL) including red, green, and blue has been performed since the 1980s.<sup>1–7</sup> With the development of manufacturing technology for nanometer materials, UCL labelling has gathered great attention.<sup>8–11</sup> The study on UCL was derived from the detection of IR light; however, it has a great number of potential applications in the fields of solid-state lasers, 3D displays, IR quantum counters, optical probes in fluorescent imaging techniques, anti-counterfeiting, NIR photocatalysis, and temperature sensors.<sup>6,7,9,10,12–15</sup> Most of UC materials are rare-earth doped solid compounds; in which, a lanthanide ion absorbs more than one photon with lower energy and converts them to one photon with higher energy by using its metastable energy levels. Yb<sup>3+</sup> ion has been extensively adopted as a sensitizer in UC processes because it has a long excited state lifetime and a relatively large absorption cross-section in the NIR region.<sup>16</sup>

No UCL from Pb<sup>2+</sup> ions have been observed until now, although the down-conversion (DC) luminescence of Pb<sup>2+</sup> ions in the UV and VIS regions has been reported and applied.<sup>17–19</sup> As we know, the absorption and emission bands of Pb<sup>2+</sup> ions usually appear in the UV region, and their electronic configuration is 6s<sup>2</sup> in the ground state (the <sup>1</sup>S<sub>0</sub> level) and (6s<sup>1</sup>)(6p<sup>1</sup>) in the excited states. The <sup>1</sup>S<sub>0</sub> ground state is expressed by <sup>1</sup>A<sub>1g</sub> and

has an even parity. The excited state expressed by (6s<sup>1</sup>)(6p<sup>1</sup>) has an odd parity and consists of triplet states (<sup>3</sup>P<sub>0</sub>, <sup>3</sup>P<sub>1</sub>, and <sup>3</sup>P<sub>2</sub>) and singlet excited state <sup>1</sup>P<sub>1</sub>. After absorbing a UV photon (~330 nm), Pb<sup>2+</sup> ion make an optical transition from <sup>3</sup>P<sub>0</sub> to <sup>1</sup>A<sub>1g</sub>.<sup>18,20</sup> The energy difference between the ground state and the triplet state of Pb<sup>2+</sup> is higher than the energy of two 980 nm photons or two excited Yb<sup>3+</sup> ions. Such an energy-level characteristic determines that neither the energy of two 978 nm photons nor the energy of an excited Yb<sup>3+</sup>-dimer (two excited Yb<sup>3+</sup> ions) can excite or sensitize a Pb<sup>2+</sup> ion efficiently. Although, in the view of energy, three-photon excitation indeed can lead to the UV UCL of Pb<sup>2+</sup> with a very low probability,<sup>16</sup> however, until now, there has been no report on the UCL of Pb<sup>2+</sup> ions under NIR excitation. Even so, the cooperative energy transfer from three or four excited Yb<sup>3+</sup> ions (Yb<sup>3+</sup>-trimer or Yb<sup>3+</sup>-tetramer) can excite Pb<sup>2+</sup> ion from the view of energy.

Cooperative transition usually means the physical processes in which identical ions or atoms simultaneously make transitions by absorbing (or emitting) one photon with the sum of all transition energies, or transferring their energies to another ion or atom. Cooperative transition includes cooperative luminescence (CL), cooperative absorption (CA), and cooperative energy transfer (CET) and is closely relative to clustered lanthanide ions in solid hosts. Clusters made of lanthanide ions can easily form in many materials, especially in alkaline-earth fluoride crystal AF<sub>2</sub> (A = Ca, Sr, Ba). When a lanthanide ion with +3 oxidation state is doped in an alkaline-earth fluoride, non-equilibrium of charge arises in the lattice due to the lanthanide ion usually occupy the position of an alkaline-earth ion with +2 oxidation state. The non-equilibrium of charge produces crystal defects such as the interstitials of F<sup>-</sup> ions and cation vacancies in order to compensate excess plus charges, which gives non-uniform distribution of lanthanide ions.

<sup>a</sup>State Key Laboratory on Integrated Optoelectronics, College of Electronic Science and Engineering, Jilin University, Changchun, Jilin 130012, China. E-mail: wpqin@jlu.edu.cn

<sup>b</sup>Yili Normal University, Electronic and Information Engineering, Laboratory on Micro-Nano Electro Biosensor and Bionic Devices, Yining, Xinjiang 835000, China



Different clusters, such as dimers, trimers, and even hexamers, can form in crystal lattices depending on the kind of lanthanide ions and their doping densities.<sup>21,22</sup> The first observations of cooperative absorption and cooperative luminescence of Yb<sup>3+</sup> dimers were reported in 1961 and 1970,<sup>23,24</sup> respectively. Since then, cooperative transitions of Yb<sup>3+</sup>-dimers have been investigated in many Yb<sup>3+</sup>-doped materials.<sup>25–27</sup> Recently, Qin *et al.* reported the triplet cooperative luminescence (TCL) at ~343 nm from three excited Yb<sup>3+</sup> ions (Yb<sup>3+</sup>-trimer) and the cooperative energy transfer from four excited Yb<sup>3+</sup> ions (Yb<sup>3+</sup>-tetramer) to one Gd<sup>3+</sup> ion, which open the way to investigate the cooperative transitions of many-body systems.<sup>28,29</sup> Furthermore, by considering the electric multipole interactions between ions and using the coupled wave functions of a many-lanthanide-ion system, Qin *et al.* proposed main cooperative transition mechanisms in a multi-ion system and calculated their probabilities.<sup>30</sup>

In the present work, we report the first experimental observation of UV UCL peaked at 383 nm from Pb<sup>2+</sup> ions sensitized by three excited Yb<sup>3+</sup> ions cooperatively.

The XRD patterns of CaF<sub>2</sub>:1% Yb<sup>3+</sup>, CaF<sub>2</sub>:0.5% Pb<sup>2+</sup> and CaF<sub>2</sub>:1% Yb<sup>3+</sup>, 0.5% Pb<sup>2+</sup> samples are shown in Fig. 1. The narrow and intense diffraction peaks indicate the well crystallization of the samples. The diffraction peaks of all the samples are consistent with the standard card (PDF #35-0816), suggesting that these materials have a cubic crystal structure.

We have measured the absorption spectra of CaF<sub>2</sub>, CaF<sub>2</sub>:0.5% Pb<sup>2+</sup>, CaF<sub>2</sub>:1% Yb<sup>3+</sup>, and CaF<sub>2</sub>:1% Yb<sup>3+</sup>, 0.5% Pb<sup>2+</sup> powder samples in a wide spectral range from 200 to 1200 nm (Fig. 2). The spectra reveal the existence of Yb<sup>3+</sup> ion (in NIR domain). The Yb<sup>3+</sup> ions are characterized by a very broad band in the NIR spectral domain, corresponding to the <sup>2</sup>F<sub>7/2</sub>–<sup>2</sup>F<sub>5/2</sub> transition (f–f transition). The ground state <sup>2</sup>F<sub>7/2</sub> split into three or four components and the excited state <sup>2</sup>F<sub>5/2</sub> split into two or three sublevels depending on the crystal field symmetry. The strongest absorption band peak appears at 979 nm.<sup>31,32</sup> Fig. 2 shows the strong “absorption” in UV region (<400 nm) should be attributed to the Mie scattering. The absorption in NIR

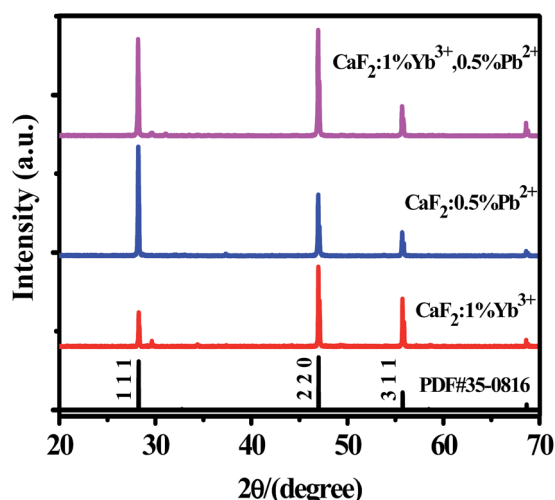


Fig. 1 XRD patterns of CaF<sub>2</sub>:x% Yb<sup>3+</sup>, y% Pb<sup>2+</sup>.

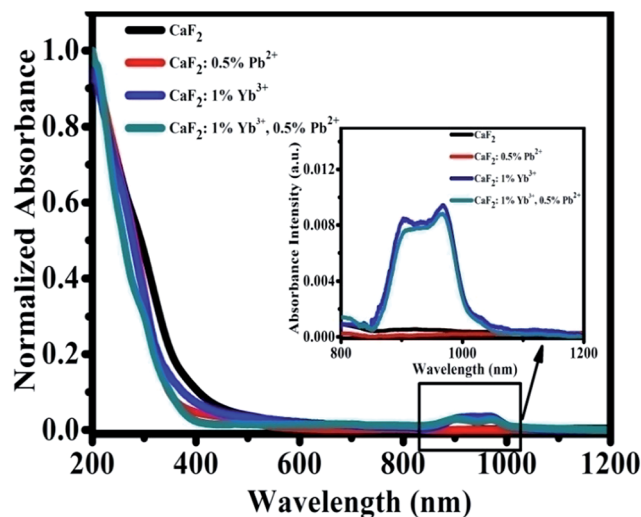


Fig. 2 Optical absorption spectra of CaF<sub>2</sub>, CaF<sub>2</sub>:0.5% Pb<sup>2+</sup>, CaF<sub>2</sub>:1% Yb<sup>3+</sup>, and CaF<sub>2</sub>:1% Yb<sup>3+</sup>, 0.5% Pb<sup>2+</sup> samples.

region show that the samples with 1% Yb<sup>3+</sup> dopant have significant absorption, and the sample of CaF<sub>2</sub>:0.5% Pb<sup>2+</sup> has not. Pb<sup>2+</sup> ions cannot absorb NIR light directly therefore cannot influence the NIR absorption spectra of Yb<sup>3+</sup> ions.

Under the excitation of a 978 nm laser, the CaF<sub>2</sub>:Yb<sup>3+</sup> polycrystalline powders showed 343 nm and 500 nm UC emission spectra, which has been previously reported.<sup>28</sup> Our previous works has demonstrated that the 343 nm UC fluorescence is the TCL of Yb<sup>3+</sup>-trimers, as shown in Fig. 3(a). With the increase of doped Yb<sup>3+</sup> concentration, the UV emission peaked at 343 nm first increases and then decreases, Fig. 3(b). The maximum UC emission intensity of Yb<sup>3+</sup>-trimers is obtained at the concentration of Yb<sup>3+</sup> reaches 1 mol%. Spectral analysis indicated that the 500 nm UC emission came from Yb<sup>3+</sup>-dimers in the CaF<sub>2</sub>:Yb<sup>3+</sup> polycrystalline, as shown in Fig. 3(c). With the increase of doped Yb<sup>3+</sup> concentration, the maximum UC emission intensity of Yb<sup>3+</sup>-dimers is obtained at the concentration of Yb<sup>3+</sup> reaches 1 mol%, Fig. 3(d).

Under 978 nm excitation, the UV emission spectra of CaF<sub>2</sub>:x% Yb<sup>3+</sup>, y% Pb<sup>2+</sup> (x = 0, 1; y = 0, 0.3, 0.5, 1, 2, 3, 4) were recorded at room temperature, as shown in Fig. 4(a). No luminescence can be found in the sample of CaF<sub>2</sub>:0.5% Pb<sup>2+</sup> throughout the entire spectral region because the NIR excitation cannot be absorbed by Pb<sup>2+</sup> ions.<sup>33</sup> On the other hand, an obvious UV fluorescence peaked at 343 nm can be seen in the spectrum of CaF<sub>2</sub>:1% Yb<sup>3+</sup>. Our previous works has demonstrated that the 343 nm upconversion fluorescence is the TCL of Yb<sup>3+</sup>-trimers.<sup>28</sup> After doping small amounts of Pb<sup>2+</sup> ions (e.g. 0.3%) in CaF<sub>2</sub>:1% Yb<sup>3+</sup>, the TCL intensity became lower and a new UV luminescence appeared at 383 nm. Fig. 4(a) show the cooperative upconversion spectra against Pb<sup>2+</sup> concentrations. It is quite clear that the TCL (343 nm) peak follow a similar trend, that is, a gradual decrease in the emission intensities until they disappear when Pb<sup>2+</sup> concentration reaches 4 mol%. With the increase of doped Pb<sup>2+</sup> concentration, the UV emission peaked at 383 nm first increases and then decreases. It reaches



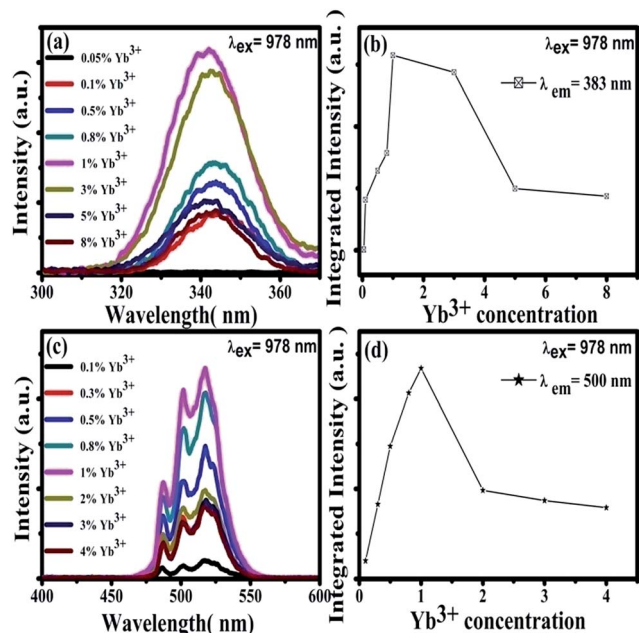


Fig. 3 (a) Emission spectra (300–400 nm) of  $\text{CaF}_2:x\% \text{Yb}^{3+}$  ( $x = 0.05, 0.1, 0.5, 0.8, 1, 3, 5, 8$ ) upon 978 nm excitation at room temperature. (b) Integrated intensity dependence of 343 nm UC emissions on the doping concentration of  $\text{Yb}^{3+}$ . (c) Emission spectra (400–600 nm) of  $\text{CaF}_2:x\% \text{Yb}^{3+}$  ( $x = 0.1, 0.3, 0.5, 0.8, 1, 2, 3, 4$ ) upon 978 nm excitation at room temperature. (d) Integrated intensity dependence of 500 nm UC emissions on the doping concentration of  $\text{Yb}^{3+}$ .

the maximum at 0.5 mol% doping concentration of  $\text{Pb}^{2+}$  ions and disappears at 4 mol%  $\text{Pb}^{2+}$  ions. Therefore, it is reasonable for us to deduce that the emission peaked at 383 nm comes from the excited  $\text{Pb}^{2+}$  ions, and further investigation (show later) exhibits that it comes from the  $^3\text{P}_0 \rightarrow ^1\text{A}_{1g}$  transition of  $\text{Pb}^{2+}$  ions. Now, the problem is, in this system, what induces the  $\text{Pb}^{2+}$  ions excited under the NIR irradiation? In ref. 28, we reported the UV UCL from  $\text{Gd}^{3+}$  ions upon 978 nm excitation and verified that the excitation of  $\text{Gd}^{3+}$  ions came from the cooperative energy transfer of four excited  $\text{Yb}^{3+}$  ions ( $\text{Yb}^{3+}$ -tetramer). In the case of  $\text{Pb}^{2+}$  ions, the same mechanism is also existence; namely, the excitation of  $\text{Pb}^{2+}$  ions may originate from the cooperative sensitization of  $\text{Yb}^{3+}$ -trimers or  $\text{Yb}^{3+}$ -tetramers.

We have already shown that the cooperative transition probability of an  $\text{Yb}^{3+}$ -trimer is much higher than that of an  $\text{Yb}^{3+}$ -tetramer,<sup>30</sup> indicating that it has a larger possibility for excited  $\text{Yb}^{3+}$ -trimers to transfer their energy to the  $\text{Pb}^{2+}$  ions than that for excited  $\text{Yb}^{3+}$ -tetramers. Moreover, it can be seen from Fig. 4(a) that the increase of  $\text{Pb}^{2+}$  concentration induces not only the fluorescence of  $\text{Pb}^{2+}$  ions but also the decrease of TCL from  $\text{Yb}^{3+}$ -trimers. Combining the above experimental phenomena with the fact that  $\text{Pb}^{2+}$  ions cannot absorb 978 nm excitation light directly, it is not difficult to deduce that the excitation of  $\text{Pb}^{2+}$  ions originates from the cooperative sensitization of more than two excited  $\text{Yb}^{3+}$  ions, in other words, from the cooperative energy transfer of  $\text{Yb}^{3+}$ -trimers. It can be seen from Fig. 4(a) that the increment of  $\text{Pb}^{2+}$  luminescence is much smaller than the decrement of TCL, indicating that not all

excitation energy of  $\text{Yb}^{3+}$ -trimers lost in the energy transfer to  $\text{Pb}^{2+}$  ions. The UV emissions of 343 nm and 383 nm completely disappear when the doping concentration of  $\text{Pb}^{2+}$  ions reaches 4%, which strongly suggests that doped  $\text{Pb}^{2+}$  ions lead to the occurrence of cooperative energy transfer from  $\text{Yb}^{3+}$ -trimers. According to above analysis, we propose here that the excitation of  $\text{Pb}^{2+}$  ions comes from the energy transfer from excited  $\text{Yb}^{3+}$ -trimers.

Furthermore, we studied the influence of  $\text{Pb}^{2+}$  concentration to the cooperative luminescence from  $\text{Yb}^{3+}$ -dimers (DCL). As shown in Fig. 4(b), the intensity of green DCL from  $\text{Yb}^{3+}$ -dimers becomes lower when the concentration of  $\text{Pb}^{2+}$  ions increases gradually. The DCL emission band in the green spectral region has unique spectral structure even at room temperature. When the doping concentration of  $\text{Pb}^{2+}$  ions increases gradually from 0% to 6% in  $\text{CaF}_2:1\% \text{Yb}^{3+}$  samples, the DCL decreases and until completely disappears at 6%  $\text{Pb}^{2+}$  doping concentration. The transition probabilities of DCL and TCL in  $\text{CaF}_2$  are calculated to be  $2.6 \times 10^{-2} \text{ s}^{-1}$  and  $1.8 \times 10^{-6} \text{ s}^{-1}$ , respectively.<sup>30</sup> Although the TCL from  $\text{Yb}^{3+}$ -trimers disappears when the doped concentration of  $\text{Pb}^{2+}$  ions is 4%, the DCL from  $\text{Yb}^{3+}$ -dimers exists until the doping concentration of  $\text{Pb}^{2+}$  ions reaches 6%. Fig. 4(c) shows the temperature-dependent UC emission spectra of  $\text{CaF}_2:1\% \text{Yb}^{3+}, 0.5\% \text{Pb}^{2+}$  during cooling under the excitation of a 978 nm laser. As the temperature decreases, the peak positions of all emission bands (343 and 383 nm) exhibit no significant changes, whereas the UC emission intensities increase monotonously. It is well known that the

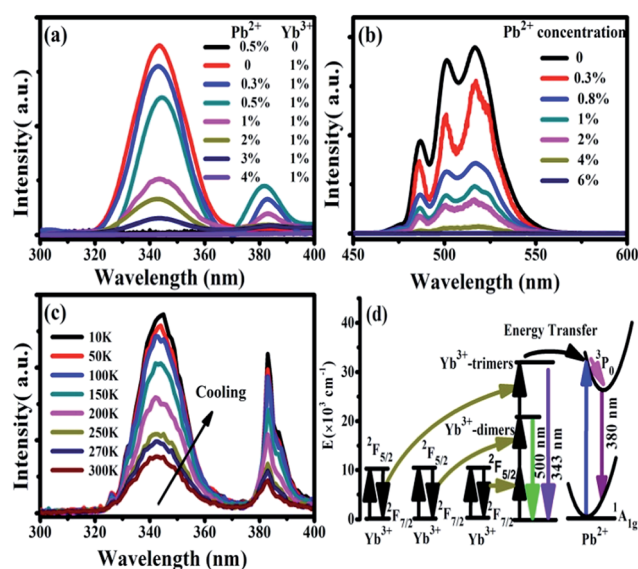


Fig. 4 (a) Emission spectra (300–400 nm) of  $\text{CaF}_2:x\% \text{Yb}^{3+}, y\% \text{Pb}^{2+}$  ( $x = 0, 1; y = 0, 0.3, 0.5, 1, 2, 3, 4$ ) upon 978 nm excitation at room temperature (b) emission spectra (450–600 nm) of  $\text{CaF}_2:1\% \text{Yb}^{3+}, y\% \text{Pb}^{2+}$  ( $y = 0, 0.3, 0.8, 1, 2, 4, 6$ ) upon 978 nm excitation at room temperature (c) temperature dependent UC emission spectra of  $\text{CaF}_2:1\% \text{Yb}^{3+}, 0.5\% \text{Pb}^{2+}$  during cooling (d) schematic energy level diagram of  $\text{Yb}^{3+}$  and  $\text{Pb}^{2+}$ . The cooperative energy transfer from three excited  $\text{Yb}^{3+}$  ions to one  $\text{Pb}^{2+}$  ion is exhibited by using black arrows. The magenta arrow indicates the non-radiative relaxation process in  $\text{Pb}^{2+}$  ions.



luminescence efficiencies are strongly temperature dependent, and usually the higher temperature would result in lower luminescence efficiency due to the strong nonradiative loss as the temperature rises. Fig. 4(d) shows a schematic of energy diagram for the cooperative energy transfer of three  $\text{Yb}^{3+}$  ions. In the schematic diagram,  $\text{Pb}^{2+}$  ions are excited by the sensitization of  $\text{Yb}^{3+}$ -trimers, and then relax to the bottom of the excited state through a non-radiative way. When the excited  $\text{Pb}^{2+}$  ions make a transition from the excited state  $^3\text{P}_0$  to the ground state  $^1\text{A}_{1g}$ , the UC emission at 383 nm can be observed. The cooperative UC process includes four ions, one  $\text{Pb}^{2+}$  ion and three  $\text{Yb}^{3+}$  ions. Under the excitation of 978 nm NIR, the multi-ion system emits an UV photon of 383 nm. The  $^3\text{P}_0 \rightarrow ^1\text{A}_{1g}$  transition of  $\text{Pb}^{2+}$  ions is forbidden since  $\Delta S = 1$  and  $\Delta J = 0$ . However, selection rules are not absolute, especially for heavy ions (such as  $\text{Pb}^{2+}$ ). In a heavy ion, the coupling of spin-orbit is strong, which mixes spin triplet ( $S = 1$ ) and singlet ( $S = 0$ ) and lifts the spin forbidden partly. As a result, the spin forbidden transitions in some heavy ions can be observed. It can be seen from Fig. 4(d) that the purple line shows the radiative transition of  $\text{Pb}^{2+}$  ions. Fig. 5 shows the intensity dependence of 343 nm, 383 nm, and 500 nm UC emissions on the doping concentration of  $\text{Pb}^{2+}$ . While the concentration of  $\text{Yb}^{3+}$  keeps at 1%, the best concentration of  $\text{Pb}^{2+}$  ions is 0.5% for the emission of  $\text{Pb}^{2+}$  ions at 383 nm.

The UV excitation spectrum of 383 nm emission from  $\text{CaF}_2:1\% \text{Yb}^{3+}, 0.5\% \text{Pb}^{2+}$  is peaked at 330 nm (due to  $\text{Pb}^{2+}$  ions), as shown in Fig. 6(a). The excitation band is highly overlapped with the TCL band peaked at 343 nm, which satisfies the condition of cooperative sensitization from excited  $\text{Yb}^{3+}$ -trimers to  $\text{Pb}^{2+}$  ions and gives further the excitation mechanism of 383 nm UCL. The 383 nm luminescence of  $\text{CaF}_2:0.5\% \text{Pb}^{2+}$  upon 330 nm excitation shows that this luminescence comes from  $\text{Pb}^{2+}$  ions, as shown in Fig. 6(b). Under 330 nm excitation, we also recorded the UV emission spectrum of  $\text{CaF}_2:1\% \text{Yb}^{3+}, 0.5\% \text{Pb}^{2+}$  (red line). This spectral result is similar to that of the

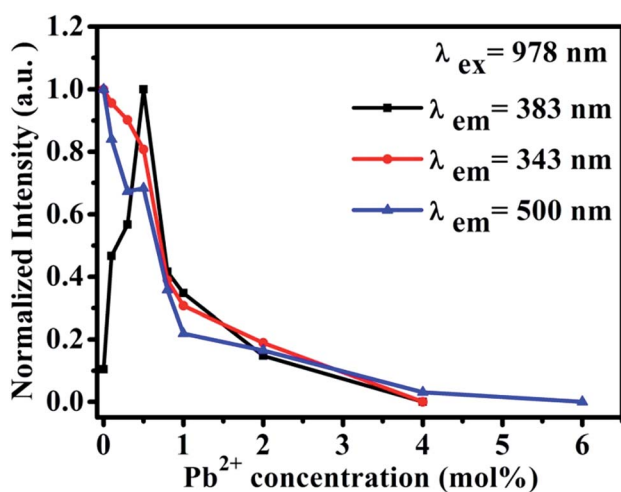


Fig. 5 Intensity dependence of 343 nm, 383 nm and 500 nm UC emissions on the doping concentration of  $\text{Pb}^{2+}$  in  $\text{CaF}_2:1\% \text{Yb}^{3+}, x\% \text{Pb}^{2+}$  ( $x = 0, 0.3, 0.5, 0.8, 1, 2, 3, 4, 6$ ).

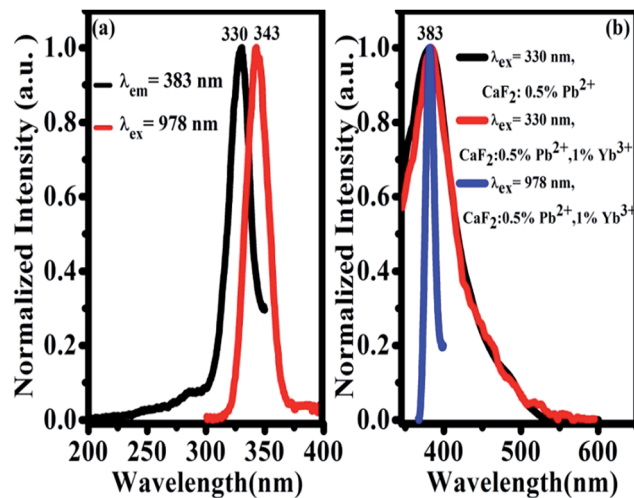


Fig. 6 (a) UC emission spectrum upon 978 nm excitation of  $\text{Yb}^{3+}$ -trimers (red line) and excitation spectrum for 383 nm  $\text{Pb}^{2+}$  emission in  $\text{CaF}_2:1\% \text{Yb}^{3+}, 0.5\% \text{Pb}^{2+}$  (black line) at room temperature; (b) emission spectra of  $\text{CaF}_2:0.5\% \text{Pb}^{2+}$  (black) and  $\text{CaF}_2:1\% \text{Yb}^{3+}, 0.5\% \text{Pb}^{2+}$  (red) upon 330 nm excitation, and the UCL spectrum of  $\text{CaF}_2:1\% \text{Yb}^{3+}, 0.5\% \text{Pb}^{2+}$  (blue) upon 978 nm excitation at room temperature, respectively.

sample without  $\text{Yb}^{3+}$  doping, indicating that the down-conversion emission of  $\text{Pb}^{2+}$  ions is not influenced by  $\text{Yb}^{3+}$  doping. The absorption bands of  $\text{Pb}^{2+}$  ions in  $\text{CaF}_2$  are peaked at 246 nm, 306 nm, and a broad band between 310 nm and 450 nm.<sup>33</sup> On the other hand, upon 978 nm NIR excitation, a similar UV emission (Fig. 6(b), blue line) peaked at 383 nm was also observed in  $\text{CaF}_2:1\% \text{Yb}^{3+}, 0.5\% \text{Pb}^{2+}$ . Therefore, it is reasonable for us to attribute the UV emission peaked at 383 nm to the  $^3\text{P}_0 \rightarrow ^1\text{A}_{1g}$  transition of  $\text{Pb}^{2+}$  ions. The widths of black and red peaks are almost the same and wider than that of the blue one. There are various activator symmetry sites for the codoped  $\text{Pb}^{2+}$  ions in the powder samples but only a special part of them can be excited by the ET from the excited  $\text{Yb}^{3+}$ -trimers, therefore the UCL band from  $\text{Pb}^{2+}$  ions is rather narrow.

In order to study the cooperative energy transfer from  $\text{Yb}^{3+}$ -trimers to  $\text{Pb}^{2+}$  ions, we studied the excited state dynamics of  $\text{CaF}_2:1\% \text{Yb}^{3+}, 0.5\% \text{Pb}^{2+}$  under the excitation of 978 nm. At 10 K and 300 K, we recorded the decay curve of TCL from  $\text{CaF}_2:1\% \text{Yb}^{3+}, 0.5\% \text{Pb}^{2+}$  under the chopped 978 nm excitation by using an oscilloscope. The energy transfer processes are often dependent on temperature. It can be seen from Fig. 7(a) that these decay curves have no rising edge, which indicates that TCL ( $\sim 343$  nm) come from the direct excitation of 978 nm and no energy transfer process exists. The lifetime of  $\text{Yb}^{3+}$ -trimers a little decrease from 0.487 ms to 0.423 ms. In addition, the higher the temperature the shorter the life time due to dependence of nonradiative multiphonon relaxation processes on temperature. However, the 383 nm UCL of  $\text{Pb}^{2+}$  ions shows a rising edge, as shown in Fig. 7(b), which means that the excitation of  $\text{Pb}^{2+}$  comes from energy transfer. The lifetime of  $\text{Pb}^{2+}$  excited state is long (0.475 ms) due to the  $^3\text{P}_0 \rightarrow ^1\text{A}_{1g}$  transition is strongly forbidden. As can be seen in Fig. 7(c), the lifetime of TCL gradually decreases with the increase of  $\text{Pb}^{2+}$



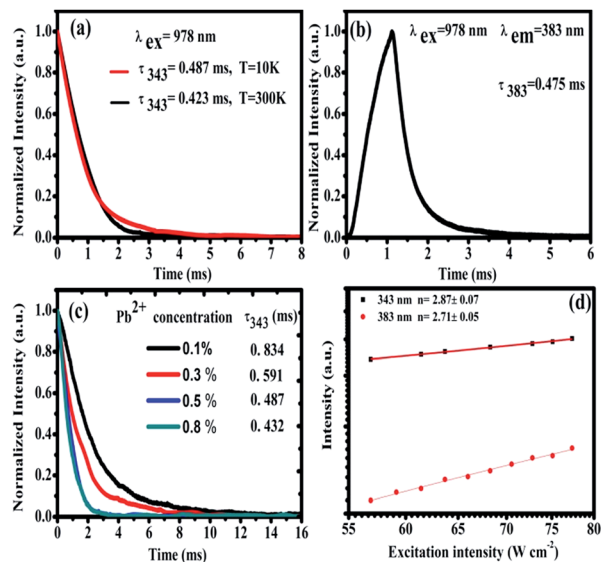


Fig. 7 (a) Temperature dependent fluorescence decay curves of 343 nm TCLs. (b) Fluorescence decay curve of the UCL at 383 nm from  $\text{Pb}^{2+}$  ions upon 978 nm excitation at 10 K. (c) Fluorescence decay curves of 343 nm TCL from  $\text{Yb}^{3+}$ -trimers with different  $\text{Pb}^{2+}$  concentrations under 978 nm excitation in  $\text{CaF}_2:1\% \text{Yb}^{3+}, x\% \text{Pb}^{2+}$  ( $x = 0.1\%, 0.3\%, 0.5\%$ , and  $0.8\%$ ) at 10 K, respectively. (d) Double-logarithmic plots of the pump-power dependent UC emission intensity recorded under 978 nm excitation.

doping concentration, which indicates the cooperative energy transfer from  $\text{Yb}^{3+}$ -trimers to  $\text{Pb}^{2+}$  ions. Fig. 7(d) shows the typical double-logarithmic plots of luminescence intensity  $I_f$  versus the pump power density  $I_{\text{NIR}}$ . The  $n$  value can be obtained from the slope of the linear fit. The fitting results of square and circle are approximately  $2.87 \pm 0.07$  and  $2.71 \pm 0.05$  for 343 and 383 nm emissions, respectively. These  $n$  values reveal that both the emissions at 343 and 383 nm belong to three-photon UC processes.

## Conclusions

In summary, we synthesized  $\text{CaF}_2:\text{Pb}^{2+}, \text{Yb}^{3+}$  phosphors through a coprecipitation method. Under the excitation of 978 nm, not only the TCL at 343 nm from  $\text{Yb}^{3+}$ -trimers was observed but also the UV UCL at 383 nm from  $\text{Pb}^{2+}$  ions was recorded for the first time. Experimental results shows that the population of  $\text{Pb}^{2+}$  excited states originates from the cooperative energy transfer from excited  $\text{Yb}^{3+}$ -trimers. With the increase of  $\text{Pb}^{2+}$  concentration, both of the TCL and the UV UCL from  $\text{Pb}^{2+}$  ions decrease and disappear.

## Experimental section

Powder samples of  $\text{CaF}_2$  doped with  $\text{Yb}^{3+}$  (0, 1 mol%) and  $\text{Pb}^{2+}$  (0, 0.3, 0.5, 0.8, 1, 2, 3, 4 mol%) were prepared by a conventional co-precipitation method by using  $\text{Ca}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$  (99%, Aladdin),  $\text{Yb}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$  (99.99%, Aladdin),  $\text{Pb}(\text{NO}_3)_2$  (99.999%, Aladdin), and  $\text{NH}_4\text{HF}_2$  (99.99%, Aladdin) as the raw materials. Firstly, standard aqueous solutions of  $0.5 \text{ mol l}^{-1}$

$\text{Yb}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ ,  $0.01 \text{ mol l}^{-1} \text{ Pb}(\text{NO}_3)_2$ , and  $0.5 \text{ mol l}^{-1} \text{ Ca}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$  were prepared. A stoichiometric amounts of  $\text{Yb}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ ,  $\text{Pb}(\text{NO}_3)_2$ , and  $\text{Ca}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$  aqueous solutions were put in a beaker with 30 min constant stirring, and then the mixture was added dropwise to  $\text{NH}_4\text{HF}_2$  aqueous solution under constant stirring for 1 h to get uniform precipitations. The obtained precipitations were then washed several times with distilled water to remove the remained  $\text{NO}_3^-$  and  $\text{F}^-$  ions. The products were dried at  $95^\circ \text{C}$  for 12 h and then calcined at  $1200^\circ \text{C}$  for 2 h in air. All the samples were synthesized under the identical conditions. The luminescence spectra were recorded with a one-meter monochromator (SPEX 1000M; HORIBA Jobin Yvon Inc., Edison, NJ, USA) equipped with an 1800 lines per mm grating. The excitation light source was a power-adjustable continuous wave laser diode (978 nm, 10 W; BWT Beijing Ltd, Beijing, China). The mean power of this excitation light source is 10 W, and the NIR laser was focused on the sample by a lens. A digital oscilloscope (DPO4104B, bandwidth 1 GHz, sampling rate  $5 \text{ GS s}^{-1}$ ; Tektronix, Shanghai, China), a power-adjustable continuous wave laser diode (CW 978 nm, 10 W), and a chopper were used to record decay curves.

## Acknowledgements

This work supported by the National Natural Science Foundation of China (NSFC) (11274139, 11474132) and the Natural Science Foundation of Xinjiang Province, China (2015211C295).

## Notes and references

- 1 A. J. Silversmith, W. Lenth and R. M. Macfarlane, Green infrared-pumped erbium upconversion laser, *Appl. Phys. Lett.*, 1987, **51**, 1977.
- 2 R. M. Macfarlane, F. Tong, A. J. Silversmith and W. Lenth, Violet cw neodymium upconversion laser, *Appl. Phys. Lett.*, 1988, **52**, 1300.
- 3 T. Danger, J. Koetke, R. Brede, E. Heumann, G. Huber and B. H. T. Chai, Spectroscopy and green upconversion laser emission of  $\text{Er}^{3+}$ -doped crystals at room temperature, *J. Appl. Phys.*, 1994, **76**, 1413.
- 4 L. F. Johnson and H. J. Guggenheim, Laser emission at  $3 \mu$  from  $\text{Dy}^{3+}$  in  $\text{BaY}_2\text{F}_8$ , *Appl. Phys. Lett.*, 1973, **23**, 96.
- 5 M. F. Joubert, Photon avalanche upconversion in rare earth laser materials, *Opt. Mater.*, 1999, **11**, 181.
- 6 J. F. Suyver, A. Aebischer, D. Biner, P. Gerner, J. Grimm, S. Heer, K. W. Kramer, C. Reinhard and H. U. Gudel, Novel materials doped with trivalent lanthanides and transition metal ions showing near-infrared to visible photon upconversion, *Opt. Mater.*, 2005, **27**, 1111.
- 7 M. Pollnau, D. R. Gamelin, S. R. Luthi and H. U. Gudel, Power dependence of upconversion luminescence in lanthanide and transition-metal-ion systems, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2000, **61**, 3337.
- 8 E. H. Song, S. Ding, M. Wu, S. Ye, F. Xiao, S. F. Zhou and Q. Y. Zhang, Anomalous NIR Luminescence in  $\text{Mn}^{2+}$ -Doped Fluoride Perovskite Nanocrystals, *Adv. Opt. Mater.*, 2014, **2**, 670.



- 9 L. L. Wang, X. J. Xue, F. Shi, D. Zhao, D. S. Zhang, K. Z. Zheng, G. F. Wang, C. F. He, R. Kim and W. P. Qin, Ultraviolet and violet upconversion fluorescence of europium(III) doped in  $\text{YF}_3$  nanocrystals, *Opt. Lett.*, 2009, **34**, 2781.
- 10 E. H. Song, S. Ding, M. Wu, S. Ye, F. Xiao, G. P. Dong and Q. Y. Zhang, Temperature-tunable upconversion luminescence of perovskite nanocrystals  $\text{KZnF}_3:\text{Yb}^{3+}, \text{Mn}^{2+}$ , *J. Mater. Chem. C*, 2013, **1**, 4209.
- 11 N. Rakov, R. B. Guimaraes and G. S. Maciel, Photon up-conversion production in  $\text{Tb}^{3+}$ - $\text{Yb}^{3+}$  co-doped  $\text{CaF}_2$  phosphors prepared by combustion synthesis, *Mater. Res. Bull.*, 2016, **74**, 103.
- 12 F. F. Huang, X. Q. Liu, Y. Y. Ma, S. Kang, L. L. Hu and D. P. Chen, Origin of near to middle infrared luminescence and energy transfer process of  $\text{Er}^{3+}/\text{Yb}^{3+}$  co-doped fluorotellurite glasses under different excitations, *Sci. Rep.*, 2015, **5**, 8233.
- 13 W. Streck, B. Cichy, L. Radosinski, P. Gluchowski, L. Marciniak, M. Lukaszewicz and D. Hreniak, Laser-induced white-light emission from graphene ceramics-opening a band gap in graphene, *Light: Sci. Appl.*, 2015, **4**, e237.
- 14 W. P. Qin, D. S. Zhang, D. Zhao, L. L. Wang and K. Z. Zheng, Near-infrared photocatalysis based on  $\text{YF}_3:\text{Yb}^{3+} \text{Tm}^{3+}/\text{TiO}_2$  core/shell nanoparticles, *Chem. Commun.*, 2010, **46**, 2304.
- 15 X. Y. Guo, W. H. Di, C. F. Chen, C. X. Liu, X. Wang and W. P. Qin, Enhanced near-infrared photocatalysis of  $\text{NaYF}_4:\text{Yb}$ ,  $\text{Tm}/\text{CdS}/\text{TiO}_2$  composites, *Dalton Trans.*, 2014, **43**, 1048.
- 16 F. Auzel, Upconversion and anti-stokes processes with f and d ions in solids, *Chem. Rev.*, 2004, **104**, 139.
- 17 C. P. Joshi and S. V. Moharil, Luminescence of  $\text{Pb}^{2+}$  in some aluminates prepared by combustion synthesis, *Phys. Status Solidi B*, 2000, **220**, 985.
- 18 H. F. Folkerts, J. Zuidema and G. Blasse, The luminescence of  $\text{Pb}^{2+}$  in lead compounds with one-dimensional chains, *Solid State Commun.*, 1996, **99**, 655.
- 19 H. F. Folkerts and G. Blasse, Two types of luminescence from  $\text{Pb}^{2+}$  in alkaline-earth carbonates with the aragonite structure, *J. Phys. Chem. Solids*, 1996, **57**, 303.
- 20 D. F. Anderson, J. A. Kierstead, P. Lecoq, S. Stollb and C. L. Woody, A search for scintillation in doped and orthorhombic lead fluoride, *Nucl. Instrum. Methods Phys. Res., Sect. A*, 1994, **342**, 473.
- 21 S. A. Kazanskii, A. I. Ryskin, A. E. Nikiforov, A. Y. Zaharov, M. Y. Ougrumov and G. S. Shakurov, EPR spectra and crystal field of hexamer rare-earth clusters in fluorites, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2005, **72**, 014127.
- 22 V. A. Chernyshev, A. E. Nikiforov and A. D. Nazemnikh, Hexamer clusters in  $\text{MeF}_2:\text{Yb}^{3+}$  ( $\text{Me} = \text{Ca}, \text{Sr}, \text{Ba}$ ), *J. Phys.: Conf. Ser.*, 2011, **324**, 012025.
- 23 E. Nakazawa, Cooperative Luminescence in  $\text{YbPO}_4$ , *Phys. Rev. Lett.*, 1970, **25**, 1710.
- 24 F. Varsanyi and G. H. Dieke, Ion-pair resonance mechanism of energy transfer in rare earth crystal fluorescence, *Phys. Rev. Lett.*, 1961, **7**, 442.
- 25 J. Wang, R. R. Deng, M. A. MacDonald, B. L. Chen, J. K. Yuan, F. Wang, D. Z. Chi, T. S. A. Hor, P. Zhang, G. K. Liu, Y. Han and X. Liu, Enhancing multiphoton upconversion through energy clustering at sublattice level, *Nat. Mater.*, 2014, **13**, 157.
- 26 X. T. Wei, J. B. Zhao, W. P. Zhang, Y. Li and M. Yin, Cooperative energy transfer in  $\text{Eu}^{3+}$ ,  $\text{Yb}^{3+}$  codoped  $\text{Y}_2\text{O}_3$  phosphor, *J. Rare Earths*, 2010, **28**, 166.
- 27 J. L. He, Z. G. Zhou, H. Zhan and A. X. Lin, Intense red fluorescence from Ho/Yb codoped tellurite glasses, *J. Non-Cryst. Solids*, 2014, **383**, 157.
- 28 W. P. Qin, Z. Y. Liu, C. N. Sin, C. F. Wu, G. S. Qin, Z. Chen and K. Z. Zheng, Multi-ion cooperative processes in  $\text{Yb}^{3+}$  clusters, *Light: Sci. Appl.*, 2014, **3**, e193.
- 29 T. Aidilibike, Y. Y. Li, J. J. Guo, X. H. Liu and W. P. Qin, Blue upconversion emission of  $\text{Cu}^{2+}$  ions sensitized by  $\text{Yb}^{3+}$ -trimers in  $\text{CaF}_2$ , *J. Mater. Chem. C*, 2016, **4**, 2123.
- 30 W. P. Qin, S. Cholnam, Z. Y. Liu, G. S. Qin and C. F. Wu, Theory on cooperative quantum transitions of three identical lanthanide ions, *J. Opt. Soc. Am. B*, 2015, **32**, 303.
- 31 W. Low, Paramagnetic and Optical Spectra of Ytterbium in the Cubic Field of Calcium Fluoride, *Phys. Rev.*, 1960, **118**, 1608.
- 32 V. Petit, P. Camy, J. L. Doualan, X. Portier and R. Moncorge, Spectroscopy of  $\text{Yb}^{3+}:\text{CaF}_2$ : From isolated centers to clusters, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2008, **78**, 085131.
- 33 I. Nicoara, M. Munteanu, N. Pecingina-Garjoaba, M. Stef, E. Preda and A. Lucaci, Dielectric spectra of doped and X-ray irradiated calcium fluoride crystals, *Phys. Status Solidi C*, 2007, **4**, 1234.

