


 CrossMark  
click for updates

 Cite this: *RSC Adv.*, 2017, 7, 8429

# Construction and enhanced photocatalytic activities of a hydrogenated TiO<sub>2</sub> nanobelt coated with CDs/MoS<sub>2</sub> nanosheets†

 Chunbo Liu,<sup>a</sup> Jibin Chen,<sup>b</sup> Huinan Che,<sup>b</sup> Kai Huang,<sup>b</sup> Paul A. Charpentier,<sup>c</sup> William Z. Xu,<sup>c</sup> Weidong Shi<sup>\*b</sup> and HongJun Dong<sup>\*b</sup>

A few-layered CDs (carbon dots)/MoS<sub>2</sub> nanosheet-coated hydrogenated TiO<sub>2</sub> (H-TiO<sub>2</sub>) nanobelt heterostructures—referred to as CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub>—with a flexible three-dimensional (3D) hierarchical configuration were prepared *via* a facial hydrothermal reaction. Note that the visible photocatalytic activity of H-TiO<sub>2</sub> was improved compared with that of pristine rutile TiO<sub>2</sub>, which can be mainly attributed to the optical absorption and charge carrier trapping of oxygen vacancies and Ti<sup>3+</sup> ions in TiO<sub>2</sub> nanobelts created by the hydrogenation. The CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> ternary photocatalysts exhibit excellent UV and visible photocatalytic property. *Via* optimizing the proportion of each component, the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> composite showed the highest photocatalytic degradation activity when the content of the CDs/MoS<sub>2</sub> co-catalyst was 5.0 wt% and the content of CDs in this cocatalyst was 25%. Further study revealed that the considerable photodegradation rate under UV irradiation and a large promotion of the photocatalytic activity in both the visible and near-infrared (NIR) region originated from the synergistic effect of oxygen vacancies, interfacial modification, and the vectorial charge-transfer channel design. Our study provides a desired strategy to understand and realize a rationally designed electronic transition between a semiconductor and cocatalysts, which is of great importance for the enhancement of charge separation and obtaining improved photocatalytic performance.

 Received 20th December 2016  
Accepted 28th December 2016

DOI: 10.1039/c6ra28479e

[www.rsc.org/advances](http://www.rsc.org/advances)

## 1. Introduction

As part of a high production and usage of drugs in the world, antibiotics are widely applied in the treatment of bacterial infection, but carry serious environmental concerns as they are widely discharged into the aquatic ecosystem *via* wastewater and waste treatment effluent, animal manure, and soil erosion.<sup>1,2</sup> Therefore, the elimination of tetracycline antibiotics from the aquatic ecosystem has awakened global awareness in the need to continuously improve and perfect more efficient methods to deal with their presence in the aquatic ecosystem. Titanium dioxide (TiO<sub>2</sub>), a representative species of semiconductor photocatalysts that can convert solar energy into chemical energy, has been extensively researched for environmental purification applications and in water splitting for hydrogen generation.<sup>3–6</sup> Although TiO<sub>2</sub> has a strong oxidation

strength and high chemical stability, making it suitable as a photocatalyst, its primary drawback is its wide band gap of 3.23 eV.<sup>7–11</sup> Its wide band gap means it is only active in the UV light region of the solar spectrum, which accounts for only 5% of the total incident solar energy. Therefore, conspicuous efforts have been made to extend the response spectrum of TiO<sub>2</sub> towards the visible spectral region.<sup>12–15</sup> This can be achieved by sensitizing it with narrow-band-gap semiconductors or *via* forming new donor states below the conduction band of TiO<sub>2</sub>, *e.g.* through the incorporation of metal or non-metal elements into its crystal matrix.<sup>16–18</sup> An alternative method for ameliorating the optical absorption and photocatalytic properties of TiO<sub>2</sub> is to prepare disordered nanophase TiO<sub>2</sub> through the hydrogenation of TiO<sub>2</sub> nanocrystals at 20 bar H<sub>2</sub>.<sup>19</sup> Hydrogen treatment is a more desired strategy as introducing oxygen vacancies or Ti<sup>3+</sup> incorporation into TiO<sub>2</sub> can dramatically narrow the band gap to ≈ 1.54 eV and thus enhance the visible light absorption, which consequently has attracted great interest in photocatalysis.<sup>20,21</sup> Mao's group reported that the optical absorption of hydrogenated TiO<sub>2</sub> nanocrystals shifted from ultraviolet light to the near infrared (NIR), accompanied by the appearance of oxygen vacancies and Ti<sup>3+</sup> (Ti<sup>3+</sup>/oxygen vacancies).<sup>19</sup> The introduced Ti<sup>3+</sup>/oxygen vacancies are believed to act as electronic charge carriers for suppressing the recombination of photogenerated electrons and holes (e–h pairs),

<sup>a</sup>Institute of Green Chemistry and Chemical Technology, Jiangsu University, Zhenjiang, 212013, People's Republic of China

<sup>b</sup>School of Chemistry and Chemical Engineering, Jiangsu University, Zhenjiang, 212013, People's Republic of China. E-mail: swd1978@ujs.edu.cn; donghongjun6698@aliyun.com; Fax: +86 511 8879 1108; Tel: +86 511 8879 0187

<sup>c</sup>Department of Chemical and Biochemical Engineering, University of Western Ontario, London, Ontario, Canada N6A 5B9

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c6ra28479e



thereby improving the photocatalytic activity of TiO<sub>2</sub>.<sup>22</sup> Therefore, hydrogen treatment is a desired strategy that can significantly enhance the photocatalytic property of TiO<sub>2</sub> nanostructures.

Considering the superiority of the two-dimensional (2D) nanolayered materials as a composition in photocatalysts, it is expected that coupling 2D layer cocatalysts with a visible light-responsive H-TiO<sub>2</sub> semiconductor may create a new type of photocatalyst with an efficient separation rate of e-h pairs, which would thus improve the photodegradation activity.<sup>23,24</sup> Accordingly, research on the nanohybrids, named “van der Waals heterostructures”, has aroused great interest. These materials are typically composed of MoS<sub>2</sub> nanoplates and others nanomaterials, formed by a layer-by-layer self-assembly.<sup>25,26</sup> Generally, this type of nanohybrid can exhibit superior photocatalytic activity by efficiently utilizing the intergrated merits of these components. Hinnemann's group concluded, through density function calculations of the free energy, that the S atoms on the exposed edges of MoS<sub>2</sub> are highly active, greatly improving the MoS<sub>2</sub>/G-CdS photocatalytic H<sub>2</sub> evolution activity.<sup>27</sup> Zhou *et al.* indicated that the matched energy band of the TiO<sub>2</sub>@MoS<sub>2</sub> heterojunction favours the charge transfer and suppresses the photoelectron-hole recombination between MoS<sub>2</sub> and TiO<sub>2</sub>, which induces the significant photocatalytic hydrogen production and photocatalytic degradation activity of organic materials.<sup>4</sup> Xiang *et al.* reported that the MoS<sub>2</sub>-graphene nanocomposite, when used as an efficient co-catalyst over TiO<sub>2</sub> nanoparticles, can help realize highly efficient hydrogen production without the need for a noble metal co-catalyst.<sup>6</sup> Despite the great efforts made so far, the study of photocatalysts based on van der Waals heterojunctions is still in its infancy. From a practical point of view, further work is needed to enhance their photoabsorption performance, enabling them to harvest a wide spectrum of sunlight, from ultraviolet to near-infrared wavelengths, and to achieve efficient solar energy conversion. Monodispersed carbon dots (CDs) retain the graphite structure with a size below 10 nm and have natural merits over other counterparts. First, a zero dimensional (0D) uniform distribution of CDs and less flocculation would be propitious to the interspaces and pathways for ions transfer over a multidimensional carbon material.<sup>28</sup> Second, CDs are thin enough so that there is no negative effect on the photoabsorption of the semiconductor.<sup>29-31</sup> Most importantly, CDs possess a broad cross-section of up-conversion emission, which means they can realize a better utilization of NIR light in the solar spectrum.<sup>12,29</sup> For example, CQDs/Ag/Ag<sub>2</sub>O (where CQDs = carbon quantum dots), CQDs/hydrogenated-gamma-TaON and a CQDs/C<sub>3</sub>N<sub>4</sub> composite successfully revealed photocatalytic activity and a photo-response ability over the photodecomposition of organic compounds, including for hydrogen evolution from water splitting.<sup>29,30,32</sup> This has given us useful enlightenment: similarly, the feasibility of applying a solution-based carbon precursor inspires the idea of forming a thin carbon coating layer on 3D nanostructures surface to absorb more sunlight and to enhance the vector transfer of photogenerated electrons.

Herein, we report the fabrication of a nano-sized layer-structured CDs/MoS<sub>2</sub> nanosheet-coated H-TiO<sub>2</sub> nanobelts with

a 3D hierarchical configuration through a facile hydrothermal method, and furthermore, we report investigations into its tetracycline (TC) degradation activities under simulated solar irradiation. The CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> composite photocatalysts showed the highest photocatalytic degradation activity for the sample containing 5% CDs/MoS<sub>2</sub> (CM) hybrid co-catalyst, consisting of 80% MoS<sub>2</sub> and 20% CDs. To be an effective photocatalyst the following strategies are needed: (1) a high surface area of 3D architectures consisting of H-TiO<sub>2</sub> nanobelts and a MoS<sub>2</sub> nanosheet as this will enhance the contact between the charge carriers and surface species; (2) the development of ultrathin MoS<sub>2</sub> nanosheets encapsulating the H-TiO<sub>2</sub> nanobelts for efficient and stable photogenerated charge separation; and (3) the formation of van der Waals heterostructures in a 3D CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> system, which would result in the further migration of electrons from MoS<sub>2</sub> to the CDs layer due to the electrical conductivity of the MoS<sub>2</sub> nanosheet.

## 2. Experimental

### 2.1 Materials

Titanium P25, sodium hydroxide (NaOH), citric acid, ethylenediamine, hydrochloric acid (HCl), sulfuric acid (H<sub>2</sub>SO<sub>4</sub>), sodium molybdate (Na<sub>2</sub>MoO<sub>4</sub>·2H<sub>2</sub>O), and L-cysteine were purchased from Sinopharm Chemical Reagent Beijing Co., Ltd.

### 2.2 Synthesis of hydrogenated TiO<sub>2</sub> (H-TiO<sub>2</sub>) nanobelts

TiO<sub>2</sub> nanobelts were synthesized by a hydrothermal process. Typically, we mixed the P25 powder (0.1 g) with an aqueous solution of NaOH (20 mL, 10 mol L<sup>-1</sup>), followed by a hydrothermal treatment at 180 °C in a 25 mL Teflon-lined autoclave for 48 h. Then, we eluted it with deionized water, followed by filtration and drying. The obtained sample was immersed in hydrochloric acid aqueous solution (0.1 mol L<sup>-1</sup>) for 48 h and then the sample was mixed with 20 mL H<sub>2</sub>SO<sub>4</sub> aqueous solution (0.02 mol L<sup>-1</sup>) and then transferred into a reaction caldron and heated at 80 °C for 2 h. Finally, the TiO<sub>2</sub> nanobelts were obtained *via* annealing at 600 °C for 2 h. After that, the TiO<sub>2</sub> nanobelts were heated to 600 °C at a ramping rate of 5 °C min<sup>-1</sup> and maintained for 5 h under a flow of hydrogen with a flow rate of 50 sccm.

### 2.3 Synthesis of the MoS<sub>2</sub>@H-TiO<sub>2</sub> nanobelts

Few-layers MoS<sub>2</sub>@H-TiO<sub>2</sub> heterostructures (5 wt% of MoS<sub>2</sub>) were prepared by a facile hydrothermal method. The formation process of the MoS<sub>2</sub>@H-TiO<sub>2</sub> heterostructures (5 wt% of MoS<sub>2</sub>) can be described as follows. Typically, 45 mg L-cysteine and 30 mg sodium molybdate (Na<sub>2</sub>MoO<sub>4</sub>·2H<sub>2</sub>O) were dissolved in 20 mL deionized water to form a transparent solution, and then 20 mg of prepared H-TiO<sub>2</sub> nanobelts were added into the solution. Next, the homogeneous solution was transferred into a Teflon-lined stainless steel autoclave and held at 200 °C for 24 h. A black product, MoS<sub>2</sub>@H-TiO<sub>2</sub> heterostructures, was collected after centrifugation and was dried at 50 °C for 12 h. For comparison, pure MoS<sub>2</sub> nanosheets powders were



synthesized under the same conditions as in the hydrothermal process but without the presence of H-TiO<sub>2</sub> nanobelts.

#### 2.4 Synthesis of the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub>

The multistep preparation process of CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> is displayed in Scheme 1. The CDs were prepared according to the literature, followed by the rotation-evaporation method.<sup>33</sup>

First, 9.8 mg of the prepared MoS<sub>2</sub>@H-TiO<sub>2</sub> heterostructures ( $W_{\text{Ti}}/W_{\text{Mo}} = 90/8$ ) was sonicated thoroughly in 20 mL DS stock solution (0.1 mg mL<sup>-1</sup>). After ultrasonication for 30 min, the mixture was transferred into a 50 mL Teflon-lined autoclave and kept at 140 °C for 24 h. To investigate the effect of the CDs/MoS<sub>2</sub> content on the photocatalytic degradation activity of H-TiO<sub>2</sub>, different amounts of CDs (according to the mass ratio of MoS<sub>2</sub> : CDs 1 : 1, 2 : 1, 4 : 1, 6 : 1 and 8 : 1, corresponding to a mass ratio of MoS<sub>2</sub> in composite of 1%, 3%, 5%, 7%, 10% and 15%) was added into the starting materials solution. The as-prepared CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> could be obtained after washing and drying at 60 °C overnight.

#### 2.5 Characterization

The morphologies of the as-obtained samples were observed using FESEM (S-4800 field emission scanning electron microscope) and TEM (Tenai G2 F30 S-Twin, FEI). XRD patterns were recorded by a powder X-ray diffraction method using a D/Max-IIIIC instrument with Cu K $\alpha$  radiation ( $\lambda = 1.54178 \text{ \AA}$ ). The Brunauer-Emmett-Teller specific surface areas ( $S_{\text{BET}}$ ) and porosity of the samples were measured at -196 °C on a TriStar II 3020 Micrometrics apparatus. Raman spectra were recorded on an IHR550 Raman microscope with 532 nm solid laser as an excitation source. FT-IR spectroscopy was recorded on a Bruker Vertex 70 spectrometer. UV-Vis absorption spectra were obtained using a UV-Vis spectrophotometer (UV-3600, Shimadzu, Japan). XPS spectra were recorded on a Thermo ESCALAB 250X (America) electron spectrometer. Time-resolved photoluminescence spectroscopy (TRPL) spectra were obtained on a Model FES 920 system with an excitation wavelength of 337 nm and a detection wavelength of 469 nm. The PL spectra were obtained on a Horiba JobinYvon Luminescence spectrometer.

#### 2.6 Photocatalytic experiments

The photodegradation experiments with a tetracycline (TC) solution (10 mg L<sup>-1</sup>) were carried out under UV, visible, and NIR light irradiation. In a typical photocatalytic experiment, 50 mg

of as-synthesized samples was dispersed in 100 mL pollutants aqueous solution (10 mg L<sup>-1</sup>). Then, the suspension was stirred in the dark for 40 min to ensure the adsorption-desorption equilibrium prior. A 250 W xenon lamp was used as the visible light source with filter glasses ( $\lambda < 420 \text{ nm}$ ). A 350 W mercury lamp was used as the UV source for photocatalysis. A 250 W infrared lamp was used as the NIR light source. At given irradiation time intervals, the residual pollution concentration was detected after centrifugation by the UV-Vis spectrophotometer at a specific wavelength. The concentration changes of TC were monitored by measuring the UV-Vis absorption of the suspensions at 357 nm using a TU-1810 UV-Vis spectrophotometer.


#### 2.7 Photoelectrochemical measurements

The photoelectric current (PC) response measurements were performed using a CHI 660B electrochemical workstation with a Pt plate and a Ag/AgCl electrode as the counter electrode and reference electrode, respectively. A 0.5 M Na<sub>2</sub>SO<sub>4</sub> aqueous solution was added to the electrolytic tank as the electrolyte. Electrochemical impedance spectroscopy (EIS) was performed in the frequency range of 10<sup>-2</sup> to 10<sup>6</sup> Hz, with the initial potential (0 V) in 0.5 M KCl solution containing 5.0 mM K<sub>3</sub>[Fe(CN)<sub>6</sub>]/K<sub>4</sub>[Fe(CN)<sub>6</sub>] under open circuit potential conditions. The working electrode was prepared on fluoride tin oxide (FTO) conductor glass. Typically, the sample powder (0.1 g), absolute ethanol (3 mL), polyvinylpyrrolidone (0.03 g) and oleic acid (30  $\mu$ L) were mixed and ultrasonicated to obtain a slurry. The slurry was spread onto the surface of an FTO plate dried at 80 °C for 2 h to improve the adhesion. A 300 W Xenon lamp with a UV cut-off filter ( $\lambda > 420 \text{ nm}$ ) was used as the light source.

## 3. Result and discussion

### 3.1 Characterization of the as-prepared photocatalysts

The TiO<sub>2</sub> nanobelts were prepared by a hydrothermal reaction of P25 in concentrated NaOH solution. Fig. S1 (ESI<sup>†</sup>) showed the TiO<sub>2</sub> nanobelts with a wide of 50–300 nm, a thickness of  $\approx 20 \text{ nm}$  and a length of several micrometres. After further hydrogenation treatment, the size and morphology remained the same, as seen in Fig. 1a. However, the colour of the TiO<sub>2</sub> powder changes from white to black. A typical SEM image of the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> heterostructures is shown in Fig. 1b and c (with 5 and 10 wt% CDs/MoS<sub>2</sub>, respectively). The thin CDs/MoS<sub>2</sub> nanosheets are uniformly *in situ* grown on the surface of the H-TiO<sub>2</sub> nanobelts and are interpenetrated with each other, forming 3D nanosheet networks. The pure MoS<sub>2</sub> nanosheets were

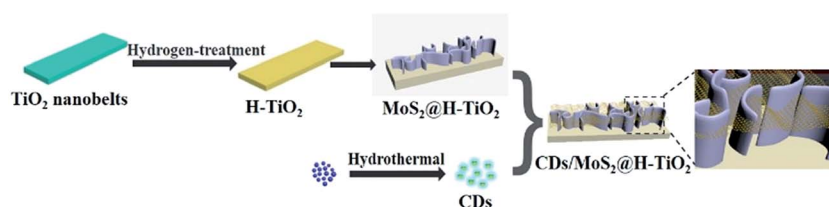

Scheme 1 Synthesis process of the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> nanocomposites.



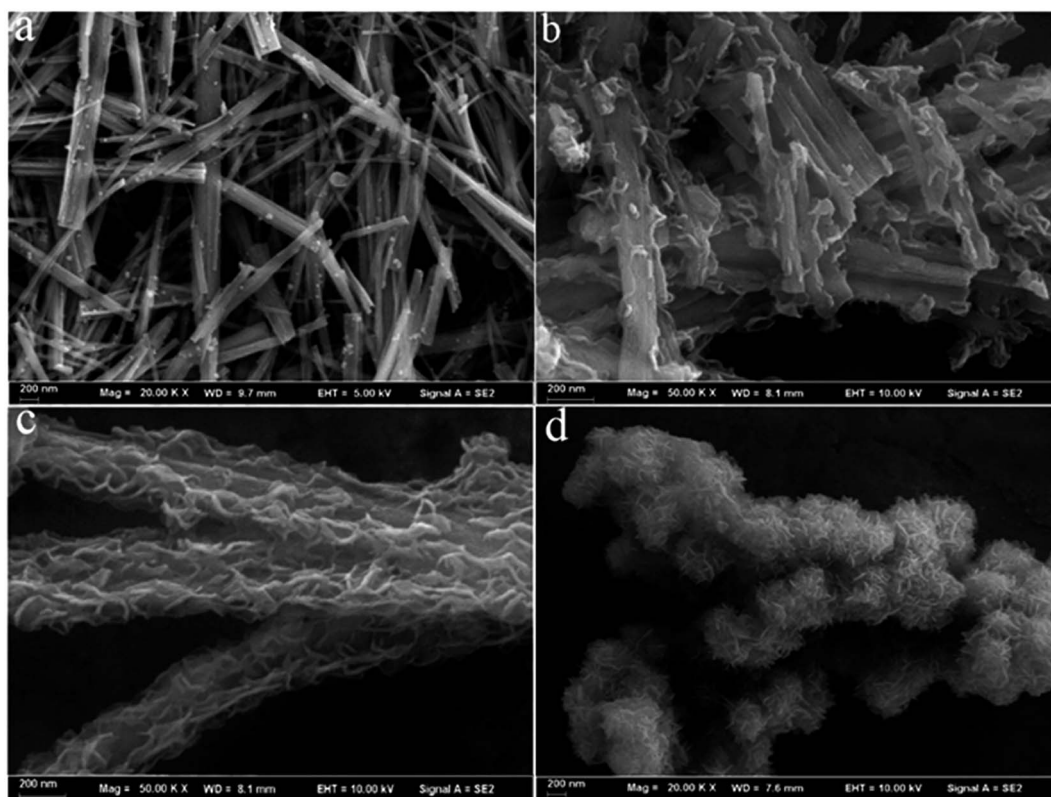


Fig. 1 SEM images of: (a) pure H-TiO<sub>2</sub> nanobelts, (b and c) CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> nanocomposite (5 wt% and 10 wt% of CDs/MoS<sub>2</sub>), and (d) pure MoS<sub>2</sub> microspheres assembled from MoS<sub>2</sub> microspheres.

also obtained by the same preparation process without the presence of H-TiO<sub>2</sub> nanobelts, self-assembled to form MoS<sub>2</sub> microsphere (Fig. 1d). However, no aggregation could be found in the SEM image of the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub>, which can be attributed to the acid etching process providing nucleation sites for the nucleation and growth of the MoS<sub>2</sub> nanosheets. Therefore, by simply increasing the precursor concentration, the density of the MoS<sub>2</sub> nanosheets in CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> can be increased significantly.

The CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> composite was characterized by powder X-ray diffraction (XRD), as shown in Fig. 2. The TiO<sub>2</sub> nanobelts and H-TiO<sub>2</sub> nanobelts exhibited similar diffraction peaks. Strong XRD diffraction peaks at  $2\theta = 25.56^\circ$ ,  $37.84^\circ$ ,  $48.15^\circ$ ,  $53.79^\circ$ ,  $55.06^\circ$  and  $62.69^\circ$  can be clearly observed, and are consistent with the (110), (101), (111), (211) and (301) crystal faces of anatase phase TiO<sub>2</sub> indexed to the JCPDS card 21-1272 with a space group of *P42/mnm* ( $a = b = 4.584 \text{ \AA}$  and  $c = 2.953 \text{ \AA}$ ). This indicated that both TiO<sub>2</sub> nanobelts and H-TiO<sub>2</sub> nanobelts displayed highly crystalline anatase phases, without other phases after hydrogenation, such as a rutile or brookite phase. Furthermore, the intensity of the peak increased after hydrogenation and the average crystal size of the H-TiO<sub>2</sub> nanobelts and TiO<sub>2</sub> nanobelts was 22.2 and 26.8 nm, respectively, as deduced from the peak broadening of the X-ray diffraction pattern using the Scherrer equation. In addition, a slight peak at 28.32 nm was observed. This peak can be attributed to the lattice oxygen on the surface of TiO<sub>2</sub> nanobelts interacting

dramatically with the hydrogen atoms when the electrons of the H atoms are transferred to the Ti<sup>4+</sup> of TiO<sub>2</sub>, which result in Ti<sup>3+</sup> defects being formed.<sup>20</sup> However, little signal attributable to the MoS<sub>2</sub> or CDs diffraction peaks can be observed in the complex samples, which may due to the low content.

Fig. 3a and b show the TEM images of CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> heterostructure, where the few-layer MoS<sub>2</sub> nanosheets cover the surface of the H-TiO<sub>2</sub> nanobelts and their thickness is about

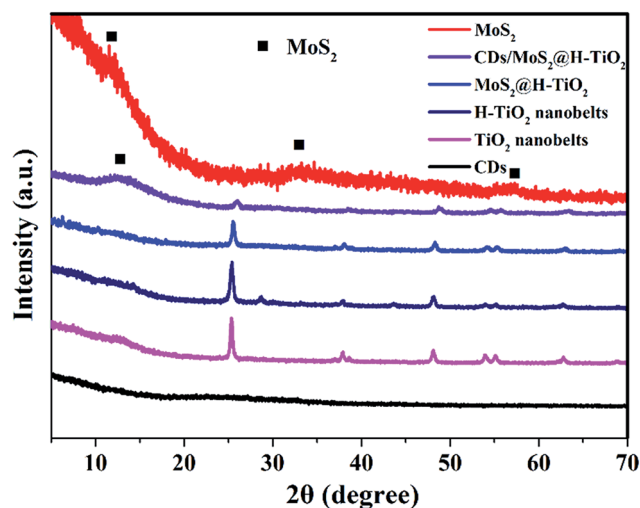


Fig. 2 XRD pattern of the as-prepared CDs, TiO<sub>2</sub>, H-TiO<sub>2</sub>, MoS<sub>2</sub>@H-TiO<sub>2</sub>, CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub>, and MoS<sub>2</sub>.



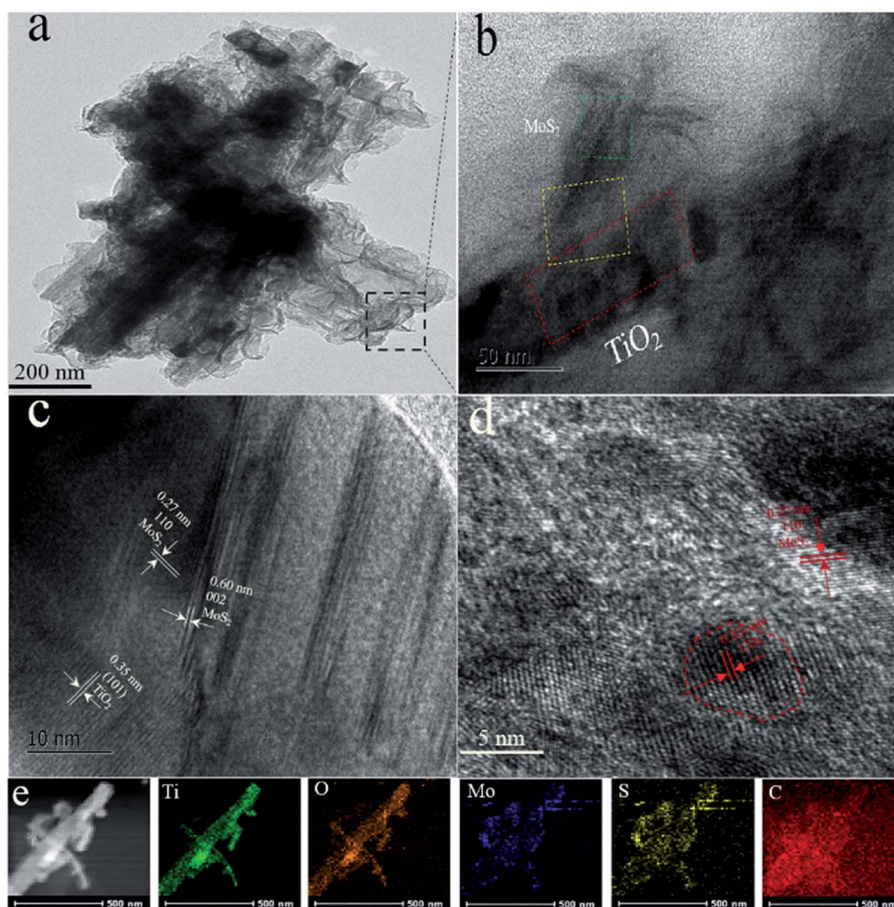


Fig. 3 (a and b) Low-magnification TEM images of CD/MoS<sub>2</sub>@H-TiO<sub>2</sub> (5 wt% of cocatalysts); (c and d) HRTEM images of the CD/MoS<sub>2</sub>@H-TiO<sub>2</sub>, and (e) EDS mapping results from CD/MoS<sub>2</sub>@H-TiO<sub>2</sub> (5 wt% of cocatalysts).

5 nm. Fig. 3c shows three type of lattice fringes: the lattice fringes with a lattice spacing of 0.35 nm correspond to the (101) facet of H-TiO<sub>2</sub>, while another set of fringe spacings around 0.27 nm can be found, which agree well with the (002) lattice spacing of the hexagonal phase MoS<sub>2</sub>. From the HRTEM images in Fig. 3d, the lattice fringes of the MoS<sub>2</sub> nanosheets can be clearly observed, suggesting the well-defined crystal structure. The fringes with a lattice spacing of 0.27 nm correspond to the (100) plane of MoS<sub>2</sub>. The (002) plane of MoS<sub>2</sub> with a lattice spacing of 0.60 nm is also observed, which comprises only 5 layers of MoS<sub>2</sub> nanosheets. The energy dispersive X-ray spectroscopy (EDS) elemental mapping from CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> also confirmed the core (H-TiO<sub>2</sub>) and the shell (CDs/MoS<sub>2</sub> nanosheets) hierarchical structures (Fig. 3e).

Fig. 4 shows the N<sub>2</sub> adsorption-desorption isotherms of the as-prepared pure H-TiO<sub>2</sub> and CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> samples. It can be seen that the CDs/MoS<sub>2</sub> shell has an effect on the specific surface area of the samples. The Brunauer-Emmett-Teller (BET) specific surface area obtained for CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> was 27.557 m<sup>2</sup> g<sup>-1</sup>, a value higher than the corresponding value, namely 13.618 m<sup>2</sup> g<sup>-1</sup>, estimated for H-TiO<sub>2</sub> nanobelts. The nanocomposites surface area increase, which indicates that the nanosheets do not restack in the composites and instead form a 3D hierarchical porous structure, as evidenced by SEM.<sup>24</sup> This

kind of 3D hierarchical structure is supposed to be beneficial for solution infiltration and photogenerated mobility, consequently improving the photocatalytic activity.

High-resolution XPS was employed to further investigate the surface binding properties of the as-synthesized samples. As illustrated in Fig. 5a (top), the Ti 2p peaks of the TiO<sub>2</sub> nanobelts are located at 460.78 and 466.03 eV, respectively, while a radically different characteristic can be found in the Ti 2p XPS spectrum of H-TiO<sub>2</sub>, which may be reasonably attributed to the formation of high density defects.<sup>20</sup> To observe these differences, a different Ti 2p XPS spectrum was obtained by subtracting the normalized spectra value of TiO<sub>2</sub> with that of the H-TiO<sub>2</sub> sample (“H-TiO<sub>2</sub>” minus “TiO<sub>2</sub>”). As illustrated in Fig. 4a (bottom), the fitting peaks at 456.78 and 462.48 eV are ascribed to Ti 2p<sub>3/2</sub> and Ti 2p<sub>1/2</sub> and should originate from Ti<sup>3+</sup> of the H-TiO<sub>2</sub> nanobelts. Similarly, the fitted result of the O 1s XPS spectrum in Fig. 4b suggests that obvious oxygen vacancies are introduced into H-TiO<sub>2</sub> *via* hydrogenation treatment (Fig. 3b). Furthermore, in terms of EPR spectroscopy (Fig. 3c), no obvious signal could be observed from the TiO<sub>2</sub> nanobelts, while the H-TiO<sub>2</sub> samples developed a noteworthy peak at *g* = 2.0010. It was thought that the above signal occurred due to the existence of oxygen vacancies in the H-TiO<sub>2</sub> nanobelts.<sup>34</sup> These results manifest that Ti<sup>3+</sup> was successfully doped into H-TiO<sub>2</sub> under the



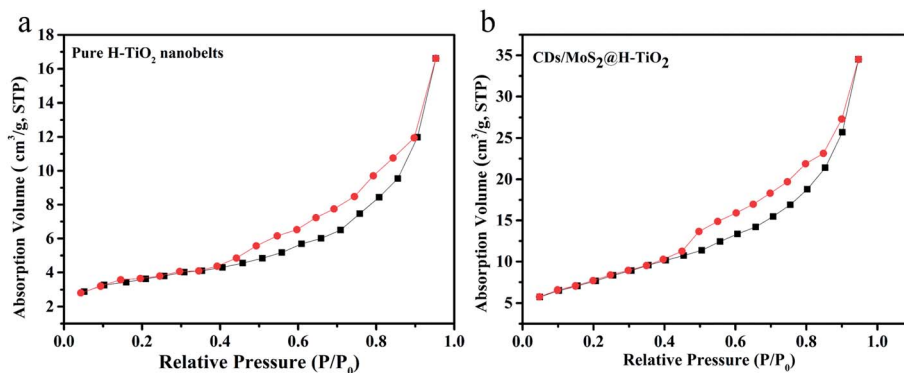


Fig. 4 BET absorption–desorption isotherms obtained of: (a) pure H-TiO<sub>2</sub> nanobelts and (b) CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> composites, in which the mass ratio of CDs to MoS<sub>2</sub> is 1 : 4 and the amount of CDs/MoS<sub>2</sub> is 5.0 wt%.

reduction atmosphere *via* taking the electrons from the hydrogen atoms and transferring them to Ti<sup>4+</sup>. The XPS spectrum (Fig. 4d) showed peaks for Ti, O, Mo, S and C, with a Mo/S atomic ratio of  $\sim 1 : 2$ , which is in good agreement with the nominal atomic composition of Mo<sub>2</sub>. The binding energies of the Mo 3d<sub>5/2</sub> and Mo 3d<sub>3/2</sub> peaks at 230.8 and 233.6 eV were observed (Fig. 4d inset), respectively, indicating that the Mo element was present in the Mo<sup>4+</sup> chemical state. In addition, the XPS spectrum of C 1s (Fig. 3e) proved the existence of CDs in the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> sample and that it efficiently combines with the MoS<sub>2</sub> to form bonds.

The UV-Vis absorption spectrum of the as-synthesized samples is shown in Fig. 6a. For the pure TiO<sub>2</sub> nanobelts, an apparent absorption in the UV region, which was coincident with the bandgap of TiO<sub>2</sub> (e.g. 3.2 eV, corresponding to  $\lambda = 387$  nm). A remarkable characteristic of the UV-Vis absorption spectra of the H-TiO<sub>2</sub> samples is the appearance of a broad and almost continuous absorption band in the visible region, which can be attributed to the low-energy photon of trapped electrons in the localized states of oxygen vacancies associated with Ti<sup>3+</sup> just below the lowest conduction band.<sup>20</sup> Adding MoS<sub>2</sub>, CDs or CDs/MoS<sub>2</sub> as cocatalysts, their light absorption was enhanced, without exception. This phenomenon may originate from the deep colour and the strong quantum confinement effect of the CDs/MoS<sub>2</sub> thin nanosheets.<sup>27</sup> The optical band gaps of pure MoS<sub>2</sub> and the CDs/MoS<sub>2</sub> nanohybrid were calculated by UV-Vis spectra. As shown in Fig. S2,† the band gap of the synthesized MoS<sub>2</sub> and CDs/MoS<sub>2</sub> were estimated to be 1.0 eV, which is narrower than that of the graphene/MoS<sub>2</sub> values reported in the previous literature (1.1–1.3 eV). This might be due to the exceptional advantages of CDs, such as high optical absorptivity. In addition, the up-converted photoluminescence spectra of the CDs under the excitation of (N)IR light were obtained (Fig. 6b). The results show that the emissions peaks are strands in the visible light wavelength of 350–600 nm. That is to say, the H-TiO<sub>2</sub> nanobelts can realize the indirect utilization of NIR by using the fluorescence effect of the CDs, so as to enhance the optical absorption response range.

To investigate in-depth the atomic structure of the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> sample, Raman and FT-IR spectroscopy were

conducted. As shown in Fig. 6c, the Raman spectra for the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> composite shows several characteristic bands at 148, 399, 518 and 639 cm<sup>-1</sup>, corresponding to the E<sub>g(1)</sub>, B<sub>1g(1)</sub>, A<sub>1g</sub> + B<sub>1g(2)</sub> and E<sub>g(2)</sub> modes of TiO<sub>2</sub>, respectively.<sup>6</sup> Interestingly, two peaks at about 1343 cm<sup>-1</sup> and 1586 cm<sup>-1</sup> were also observed, which were associated with disordered sp<sup>3</sup> carbon (D band) and conjugated sp<sup>2</sup> (G-band) of the carbon atoms.<sup>35</sup> Also, the observed D and G bands of the composite were slightly shifted compared with pure CDs, which provides further evidence for the presence of a chemical bond between the CDs and composites in the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> samples. The FT-IR spectrum was used to analyze the change in functional groups during the synthesis process. From Fig. 6d, the stretching vibrations of OH at 3430 cm<sup>-1</sup> and C–H at 2923 cm<sup>-1</sup> and 1380 cm<sup>-1</sup> can be observed. The absorption bands at 3238 cm<sup>-1</sup> and 3389 cm<sup>-1</sup> are ascribed to the O–Ti–O stretching mode and S–Mo–S bridging stretching modes, which imply the MoS<sub>2</sub> composites can efficiently combine with the H-TiO<sub>2</sub> substrate to form bonding. Based on the above description and discussion, we can conclude that the synergetic catalytic effect of the MoS<sub>2</sub> nanoplate and CDs layer by interfacial modulation plays an important role in the enhancement of photocatalytic activity.

### 3.2 Charge-transfer properties

As part of the in-depth research into the electron-assisted charge dynamics of CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub>, we also measured the time-resolved and steady-state photoluminescence spectra. As shown in Fig. 7a, the resulting fluorescence decay curves was analyzed by fitting the time-resolved fluorescence decay curves with the following multi-exponential regress model (excitation at  $\lambda = 337$  nm, for the excitation of H-TiO<sub>2</sub>):

$$I(t) = A_1 \exp(-t/\tau_1) + A_2 \exp(-t/\tau_2) \quad (1)$$

$$\tau_{\text{ave}} = (A_1\tau_1 + A_2\tau_2)/(A_1 + A_2) \quad (2)$$

where  $\tau_1$  and  $\tau_2$  are the decay times and  $A_1$  and  $A_2$  represent the relative weights of the components at  $t = 0$ .<sup>29</sup> In comparison with the TiO<sub>2</sub> nanobelts, the lifetime of H-TiO<sub>2</sub> was significantly prolonged over the lifetime of the charge carriers, which



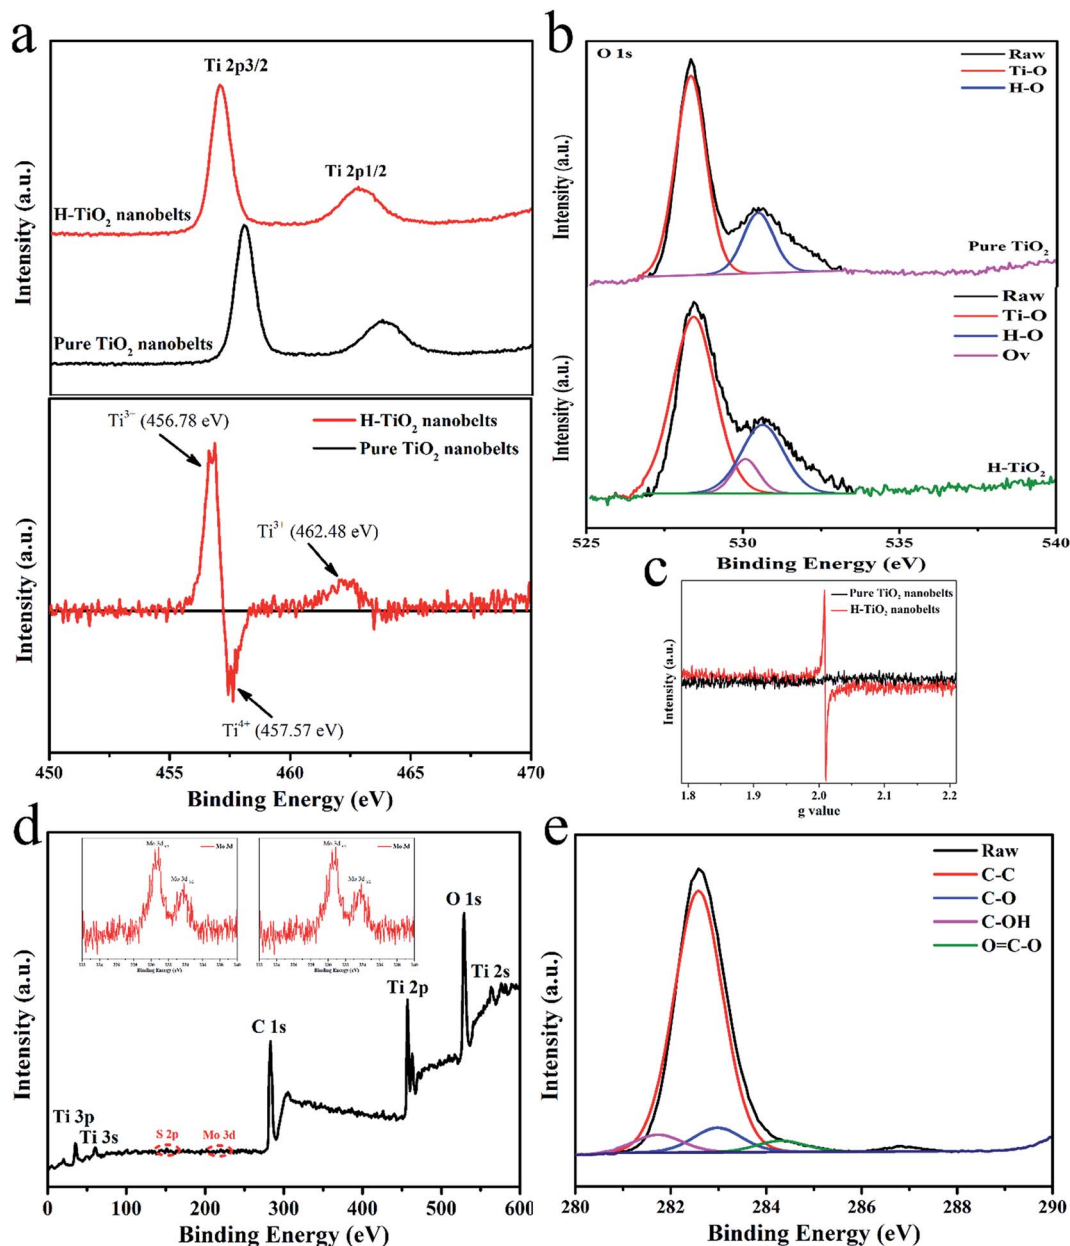


Fig. 5 (a) Original XPS spectra of Ti 2p for pure TiO<sub>2</sub> (top) and H-TiO<sub>2</sub> together with their different spectra ("H-TiO<sub>2</sub>" minus "pure TiO<sub>2</sub>") (bottom); (b) high-resolution XPS spectra of O 1s; (c) low-temperature EPR for pure TiO<sub>2</sub> and H-TiO<sub>2</sub>; (d) XPS spectrum of CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> composite and (e) XPS spectrum of C 1s.

indicates that the oxygen atoms on the surface of TiO<sub>2</sub> nanoparticles can easily be removed and an oxygen-deficient TiO<sub>2-x</sub> is generated during the hydrogenation process.<sup>20</sup> The lifetime of the as-prepared MoS<sub>2</sub>@H-TiO<sub>2</sub> nanobelts and CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> nanobelts were 0.7478 and 1.4079 ns, respectively. Notably, the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> nanobelts yielded the longest decay time as compared with the H-TiO<sub>2</sub> nanobelts and MoS<sub>2</sub>@H-TiO<sub>2</sub> nanobelts, indicating an accelerated charge transfer induced *via* the coating of the CDs/MoS<sub>2</sub> layer. Fig. 7b shows the PL emission of 1 μM RhB, where the emission peak is located at 584 nm, which is a constant independent of the excitation wavelength. The PL emission of the prepared samples

in aqueous solution can be seen in Fig. 7c, where no obvious radiation peaks were observed in any of the samples. Fig. 7d displays the steady-state PL quenching spectra of the as-synthesized samples with suspended rhodamine B aqueous solution (RhB as an indicator dye used to monitor the interfacial charge transfer) with an excitation wavelength of 337 nm. The PL emission of RhB can be quenched by H-TiO<sub>2</sub>, since the lowest unoccupied molecular orbital (LUMO) level of RhB (-1.1 V vs. NHE) is higher than the CB of H-TiO<sub>2</sub> (-0.29 V vs. NHE).<sup>36,37</sup> The H-TiO<sub>2</sub> dispersed in the RhB solution displayed a stronger PL emission than pure RhB at the emission wavelengths in the range 405–480 nm (Fig. 5d). This phenomenon



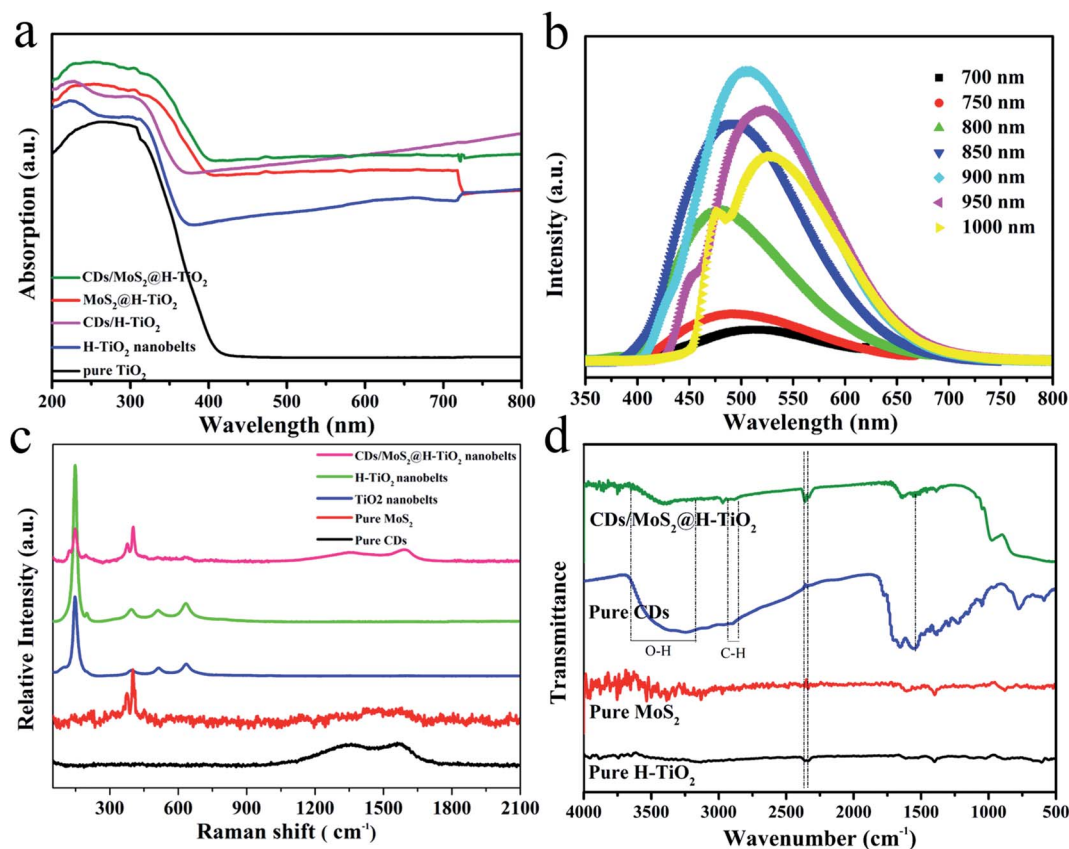


Fig. 6 (a) UV-Vis absorption spectra; (b) up-converted photoluminescence spectra of CDs; (c) Raman spectra and (d) FT-IR spectra of the prepared samples.

should be ascribed to the overlapping emission of H-TiO<sub>2</sub> and RhB. However, a weaker PL emission peak of RhB in the presence of H-TiO<sub>2</sub> was noticed for excitation wavelengths longer than 480 nm, which suggests the significance of intramolecular charge transfer. The MoS<sub>2</sub>@H-TiO<sub>2</sub> exhibited a remarkable quenching in the PL emission of RhB, considering the PL emission of MoS<sub>2</sub>@H-TiO<sub>2</sub>, indicating that the photoexcited electrons from RhB were transferred to the CB of H-TiO<sub>2</sub> as well as to the MoS<sub>2</sub> nanosheets. In particular, a remarkable depression in the PL intensity of RhB was also noted in the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> system when the excitation wavelength was shorter than 480 nm. The depression was due to the introduction of CDs, which facilitated the further transfer of electronic from the CB of MoS<sub>2</sub> to the CDs layer. As a result, a fast electron transfer *via* H-TiO<sub>2</sub> nanobelts → MoS<sub>2</sub> nanosheet → CDs layer was proved. The accelerated charge transfer is bound to reduce the recombination of photogenerated electrons-holes and enhance the photocatalytic activity.

To provide additional evidence for the kinetics of charge transfer, the transient photocurrent responses of as-prepared composites coated on the FTO substrate were measured for several cycles under visible light irradiation. Fig. 8a shows that the photocurrent increased rapidly under visible light irradiation. Meanwhile, after several periods of intermittent switching, the photocurrent still remains steady and repeatable. Compared to pure TiO<sub>2</sub> nanobelts, the H-TiO<sub>2</sub> nanobelts

displayed a higher photocurrent intensity. Previous studies have reported that surface O vacancies promote the separation of photogenerated carriers in H-TiO<sub>2</sub>. After adding MoS<sub>2</sub> or CDs cocatalysts, the photocurrent densities were significantly enhanced, indicating that the recombination of electron-hole pairs is delayed. As expected, the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> composites exhibited the highest photocurrent response, which demonstrates that constructing CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> can significantly improve the photogenerated electron-hole pair's separation. Here, the H-TiO<sub>2</sub> nanobelts not only provide a confined substrate for the *in situ* growth of few-layer MoS<sub>2</sub> nanoplates, but also form interconnected 3D conductive networks for efficiently transferring photogenerated electrons through the harness charge flow of the H-TiO<sub>2</sub> nanobelts → MoS<sub>2</sub> nanoplates → CDs layer. Additionally, electrochemical impedance spectroscopy (EIS) was employed to investigate the charge-transfer resistance of the system in the battery enclosure. As shown in Fig. 8b, the Nyquist plot indicates the charge-transfer rate occurring at the contact interface between the working electrode and the electrolyte solution. It should be noted that the H-TiO<sub>2</sub> electrode is much smaller in comparison to that of the TiO<sub>2</sub> electrode. In other words, hydrogenation treatment of the oxygen atoms on the surface of the TiO<sub>2</sub> nanobelts greatly promotes charge transfer across the electrode/electrolyte interface. Correspondingly, the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> sample shows the smallest arc radius of Nyquist curve, which shows that MoS<sub>2</sub>



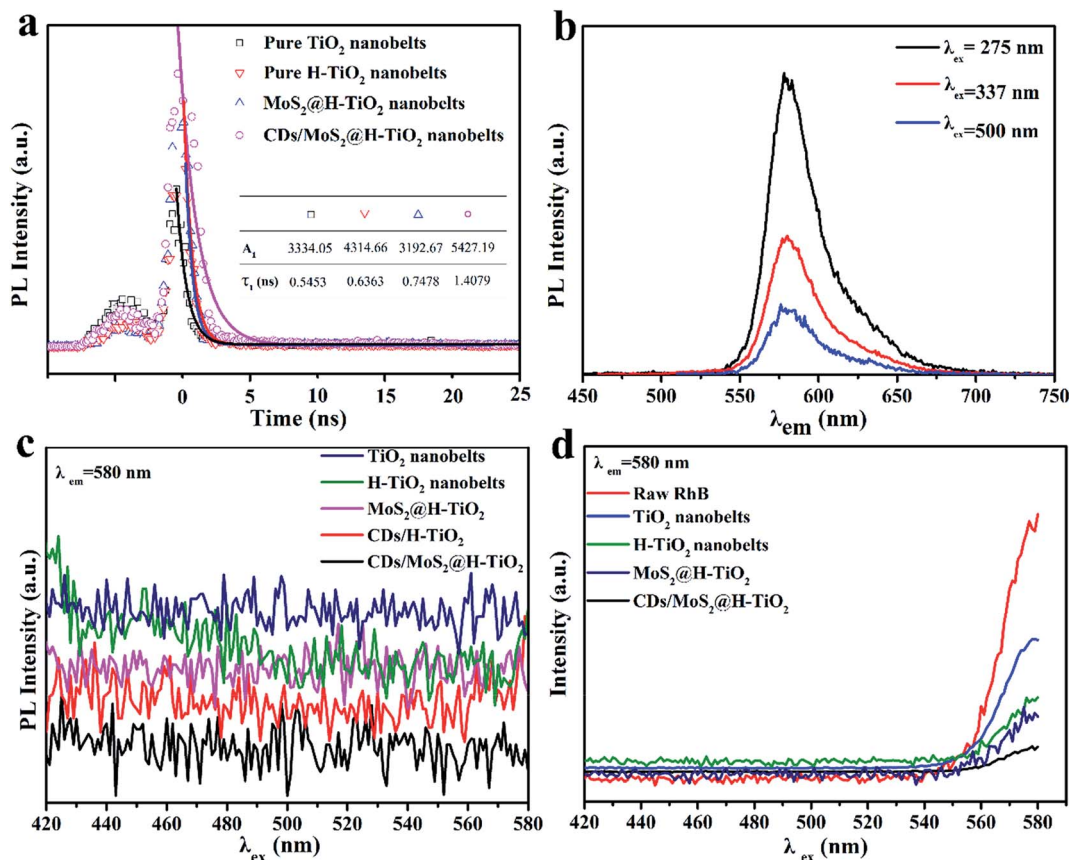


Fig. 7 (a) Time-resolved fluorescence decay curves of  $\text{TiO}_2$ ,  $\text{H-TiO}_2$ ,  $\text{MoS}_2@H\text{-TiO}_2$  and  $\text{CDs/MoS}_2@H\text{-TiO}_2$ ; (b) steady-state PL spectra of  $1 \mu\text{M}$  RhB, where the excitation wavelengths were 275, 337 and 500 nm; (c) PL emission of an aqueous solution in the presence of each sample; and (d) PL emission of an aqueous solution of  $1 \mu\text{M}$  RhB in the presence of each sample.

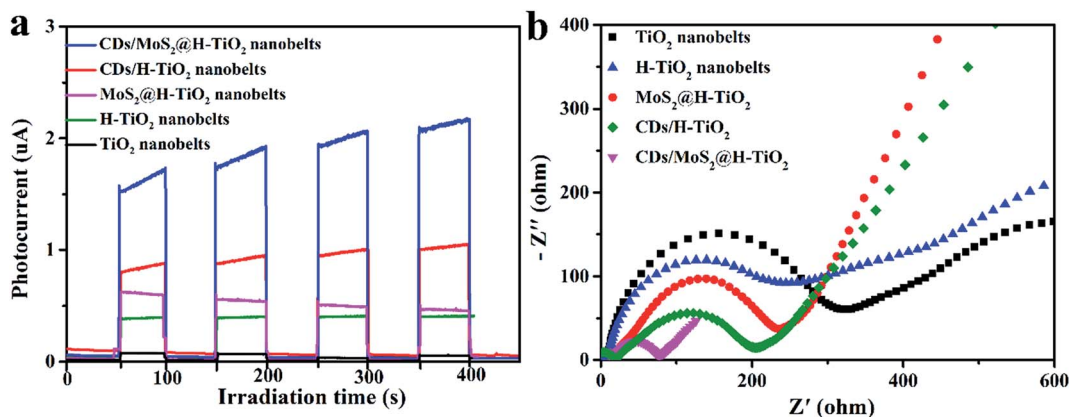


Fig. 8 Transient photocurrent response (a) and EIS (b) for  $\text{TiO}_2$ ,  $\text{H-TiO}_2$ ,  $\text{MoS}_2@H\text{-TiO}_2$ ,  $\text{CDs/TiO}_2$  and  $\text{CDs/MoS}_2@H\text{-TiO}_2$  samples.

may serve as an electron transfer medium in the vectorial electron transfer from  $\text{H-TiO}_2 \rightarrow \text{MoS}_2 \rightarrow \text{CDs}$ , thus promoting interfacial charge separation and migration, also efficiently reducing the exciton quenching and energy dissipation. In short, the PL measurements and electrochemical data demonstrate that the  $\text{CDs/MoS}_2$  nano hybrids in  $\text{CDs/MoS}_2@H\text{-TiO}_2$  could generate a notable positive synergistic effect that

significantly improves the separation of photogenerated electrons and holes.

### 3.3 Photocatalytic activity and photostability

The photocatalytic degradation activities of the aforementioned samples was carried out and the results plotted and compared in Fig. 9. Fig. 9a shows the degradation rate of TC of the



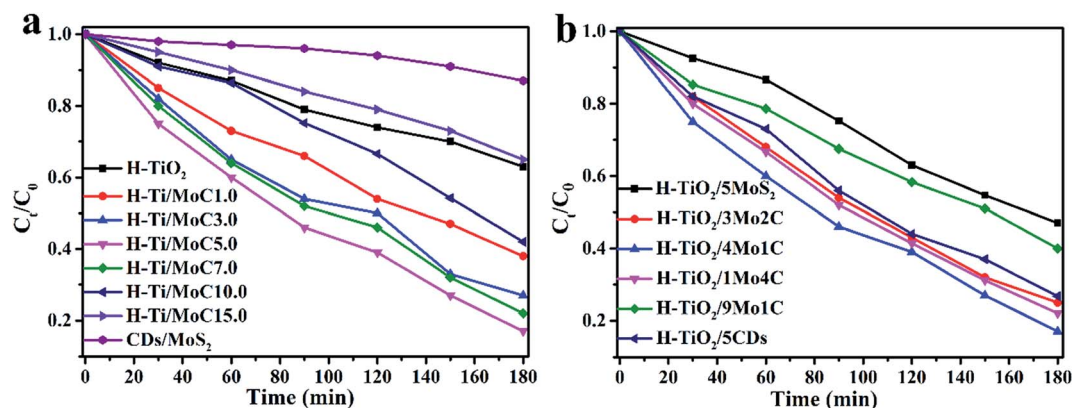


Fig. 9 Photocatalytic degradation of TC with the as-prepared samples. (a) Comparison of the photocatalytic degradation rate of different samples with different weights of cocatalysts; (b) photocatalytic degradation rate of different samples with different weight contents of CDs/MoS<sub>2</sub> in which the amount of co-catalyst is 5.0 wt%.

photocatalysts with different weight amounts of CDs/MoS<sub>2</sub> cocatalysts. It can be seen that the CDs/MoS<sub>2</sub> composites show that the photolysis of the TC molecule is very slowly, which suggests that CDs/MoS<sub>2</sub> plays the role of only a co-catalyst. Pure TiO<sub>2</sub> nanobelts show negligible activities because of the absence of optical absorption under visible light irradiation. However, the H-TiO<sub>2</sub> nanobelts exhibit obvious photocatalytic degradation activities due to the introduction of an oxygen vacancy and Ti<sup>3+</sup> in the H-TiO<sub>2</sub> nanobelts. Furthermore, the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> composites exhibit remarkable photocatalytic activities

due to the recombination delay of electron-hole pairs by the targeted electron transfer. In particular, the sample with 5.0 wt% content of CDs/MoS<sub>2</sub> nanohybrids showed the highest photocatalytic degradation activity towards TC (81.6%) within 3 h under visible light irradiation. The activities showed a gradual downward trend with the increase in the content of CDs/MoS<sub>2</sub> nanohybrids, which might be because excessive CDs/MoS<sub>2</sub> can hinder the production of active radicals by preventing the electron-hole pairs reacting with the adsorbed oxidants/reducers. Everyone knows the co-catalyst activities of MoS<sub>2</sub>

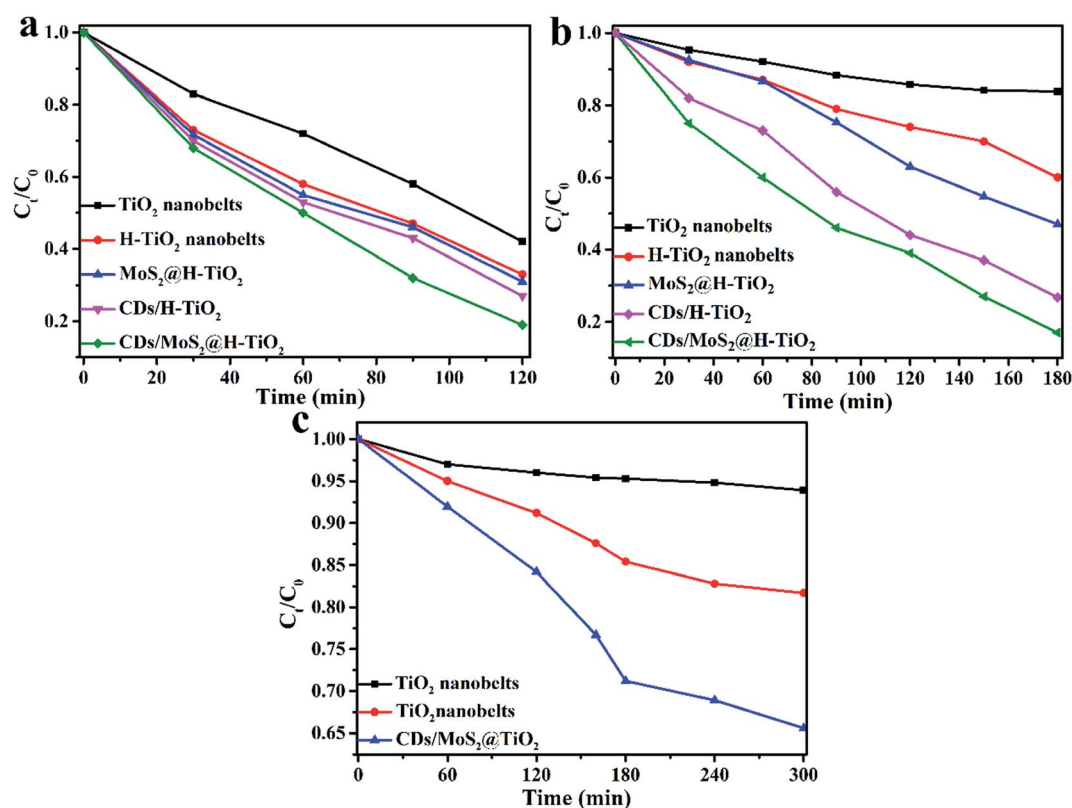


Fig. 10 Photocatalytic degradation of TC in the presence of different as-prepared photocatalysts under: (a) UV, (b) visible, and (c) NIR light irradiation.



originate from the unsaturated active S atoms on its exposed edges, while the saturated S atoms at the basal plane have no activity. Happily, the introduction of CDs can ameliorate this disadvantage due to its superior electron mobility. Obviously, as shown in Fig. 9b, the co-catalytic activity of CDs/MoS<sub>2</sub> hybrids is much better than that of pure MoS<sub>2</sub> nanosheets. The remarkably improved photocatalytic activity could be reasonably attributed to the positive synergistic effect of the CD layer and the few-layer MoS<sub>2</sub> nanosheets on the H-TiO<sub>2</sub>. After the above experiments, we demonstrated that CDs/MoS<sub>2</sub> could uniformly grow on H-TiO<sub>2</sub> when the mass ratios of CDs/MoS<sub>2</sub> to H-TiO<sub>2</sub> was 5 : 95, and this kind of composite displayed a perfect synergetic effect between the CDs and MoS<sub>2</sub>, further facilitating the electronic separation. To optimize the effects of the content of CDs/MoS<sub>2</sub> on the photodegradation activities of H-TiO<sub>2</sub>, a series of CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> composites with different mass ratios of CDs to MoS<sub>2</sub> in which the amount of the CDs/MoS<sub>2</sub> co-catalyst was 5% were investigated. From Fig. 9b, it can be seen

that all the ternary CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> composites show higher photocatalytic performance as compared with the binary MoS<sub>2</sub>@MoS<sub>2</sub> composites. For the ternary CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> nanocomposites, CDs/MoS<sub>2</sub> with a mass ratio of 1 : 4 of CDs : MoS<sub>2</sub> exhibited the highest photocatalytic activity.

To further demonstrate that the photocatalytic activity can be improved in all directions, the photocatalytic activity of CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> was evaluated for the degradation of TC under UV, visible and NIR light irradiation (Fig. 10a-c). As shown in Fig. 10a, the photodegradation efficiency of TC over the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> ternary photocatalyst was more than 80% within 120 min under UV light irradiation. The photocatalytic activity of the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> sample was superior to the others samples. This can be attributed to the oxygen vacancies and Ti<sup>3+</sup> created by the hydrogenation. The Ti<sup>3+</sup> species can serve as hole scavengers. Also, oxygen vacancies on the surface of H-TiO<sub>2</sub> can act as O<sub>2</sub> binding sites and electron scavengers, thus resisting the electron-hole pair recombination and remarkably

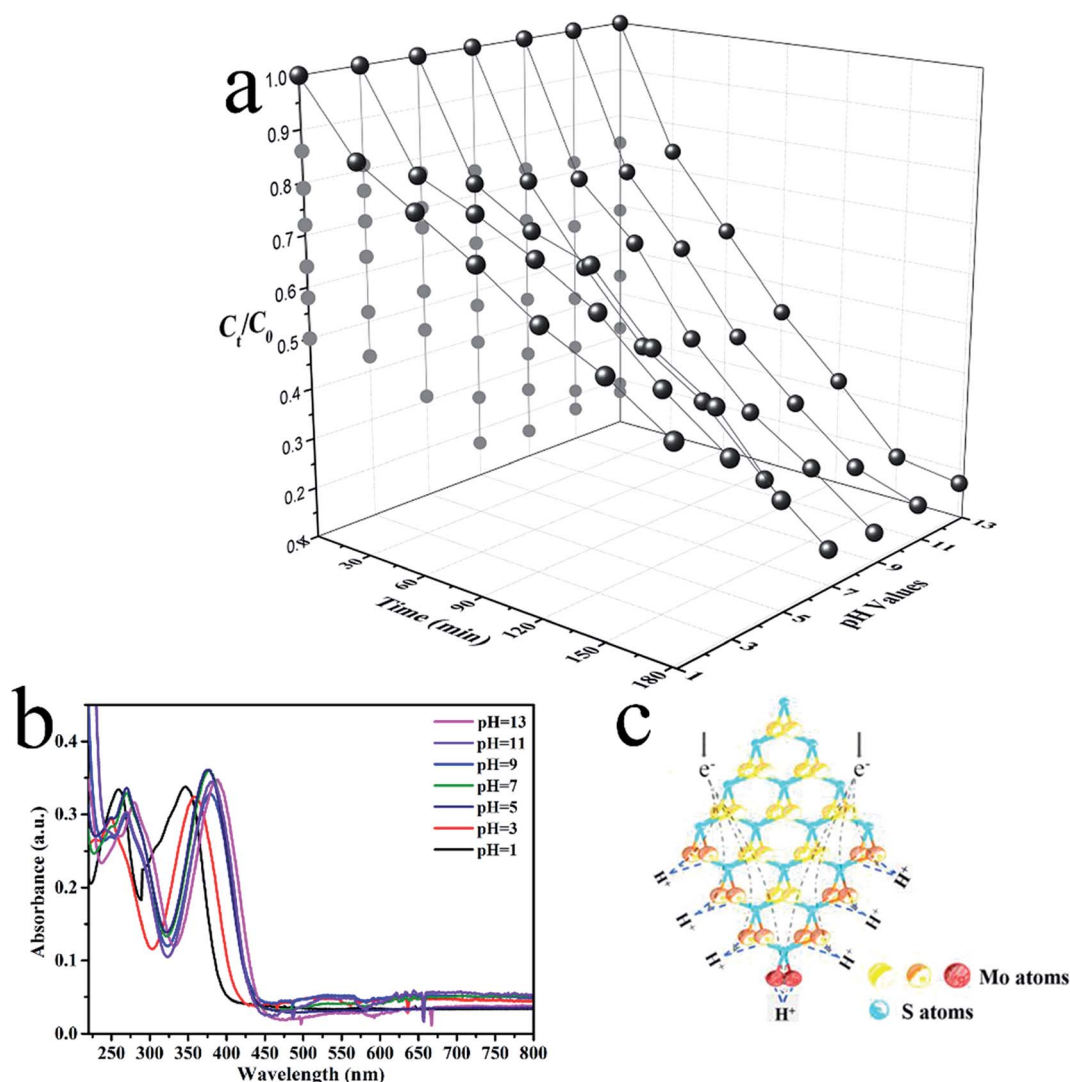


Fig. 11 (a) Photocatalytic degradation of TC at various pH conditions in the presence of CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> with visible light irradiation; (b) UV-Vis absorption spectra of TC under various pH conditions; (c) schematic of the microstructure of MoS<sub>2</sub>.



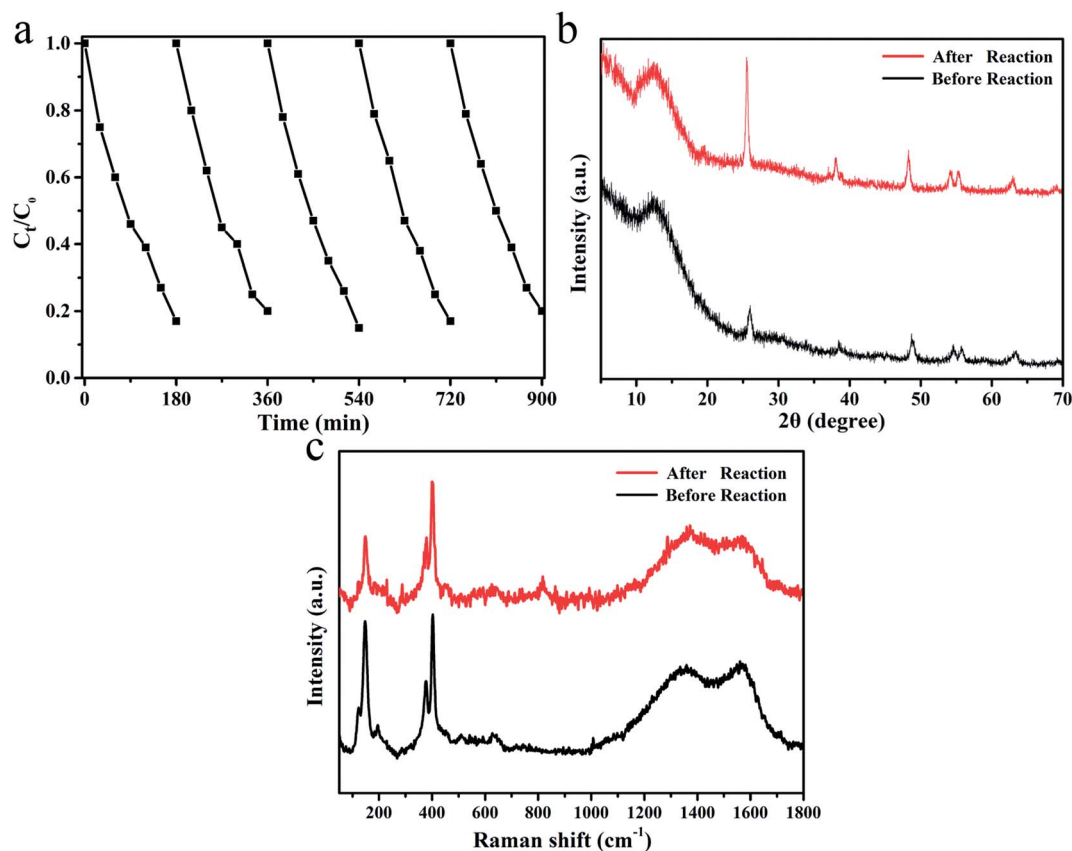


Fig. 12 (a) Five cycling experiments of CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> for TC degradation; (b) XRD pattern (b) and Raman spectrum (c) of CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> before and after 5 cycles of photocatalytic experiments.

ameliorating the photocatalytic activity of the H-TiO<sub>2</sub> nanobelts. Additionally, the visible photodegradation performance of H-TiO<sub>2</sub> was better than that of the TiO<sub>2</sub> nanobelts as well (Fig. 10b). This is because H-TiO<sub>2</sub> has intense absorption in the visible spectrum, so the solar spectrum response range has been expanded from 250 nm to about 800 nm. This guess also coincides with the above-mentioned DR tests (Fig. 6a). Under NIR light irradiation, we can see that the TC degradation degree over CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> is about 33% after 5 h. This result demonstrates that the up-converted PL effect of the CDs can play a key role in the ameliorated NIR photocatalytic performance. The NIR light is harvested by CDs, converted to visible light, and subsequently excites H-TiO<sub>2</sub> to complete the NIR photocatalysis process for the hybrid nanobelts.

Prior studies suggested that the photodegradation activity of TC was affected by the temperature and pH.<sup>38,39</sup> The pH level features most among these contributing factors. Experiments on the photodegradation of TC were carried out using CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> at pH levels between 1 and 13 to assess the effect of pH (Fig. 11a). The UV-Vis absorption spectra of TC solution under various pH conditions are shown in Fig. 11b, where it can be clearly observed that the main absorption peaks of TC-HCl are slightly red-shifted at pH below 7. Besides, the intensity of the peaks gradually decrease with time, and no additional peaks appears (Fig. S3, ESI<sup>†</sup>), indicating that the photocatalytic

reaction induced the degradation of TC and not a molecular structural change. Fig. 11a shows that the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> have a remarkable photocatalytic activity at all pH levels, but for the degradation of TC, the pH value should be as high as possible. This phenomenon could be ascribed to the presence of an unsaturated active S atom in MoS<sub>2</sub>. Hence, a diagrammatic sketch of the microstructure of MoS<sub>2</sub> and its electron reaction mechanisms in the photocatalytic process under an

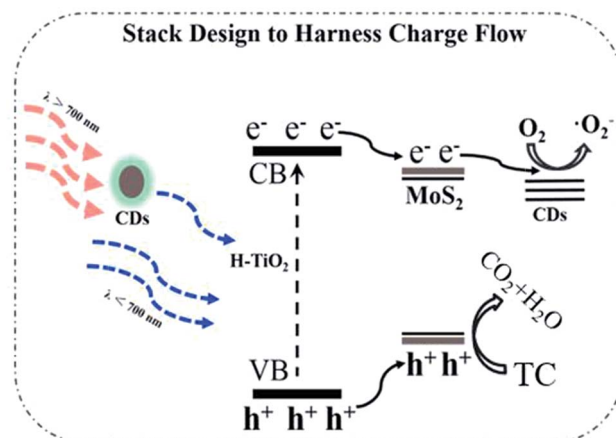


Fig. 13 Schematic of the TC photodegradation mechanism for the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> samples.



acidic environment are shown in Fig. 11c. As illustrate in Fig. 11c, different kinds of S atoms in the MoS<sub>2</sub> microstructure lead to varied catalytic activities. The unsaturated S atoms signalled by a red colour have a strong attraction to H<sup>+</sup> ions in the solution, which is higher than from the saturated atoms marked by an orange colour. Due to the abundance of H<sup>+</sup> ions in the acidic solutions, the unsaturated active S atoms expose the edges of MoS<sub>2</sub> more easily to aid capturing H<sup>+</sup> ions than in alkaline solutions, which are easily reduced by consuming a large amount of electrons. Thereby, considering the number of electrons loss in the acidic solutions, more ·O<sup>2-</sup> will be generated in the alkaline solutions. In summary, the experiments demonstrated that the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> system possesses excellent alkaline resistance and can be efficiently used for pollutant purification under alkaline conditions.

The CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> catalyst is robust, as was shown when performing repeat runs for the photocatalytic degradation of TC (pH = 7) under visible light irradiation, as shown in Fig. 12a. After five successive cycles, CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> degraded around 82% of the TC within 180 min, which is similar to the activity for the first cycle. Furthermore, the XRD and Raman patterns of before and after 5 cycles of reactions are provided in Fig. 11b and c. Notably, ever after 5 successive cycles, the as-synthesized sample showed no obvious differences, indicating its high stability and great prospect for application.

### 3.4 Possible mechanism of the photocatalytic reaction process

Based on the above results and discussion, a tentative mechanism proposed for the high photocatalytic activity of the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> composite is illustrated in Fig. 13. Under simulated sunlight irradiation, H-TiO<sub>2</sub> could absorb visible light. Simultaneously, the CDs absorb NIR light and then emit visible light (300–600 nm) as a result of up-conversion, which can in turn excite H-TiO<sub>2</sub> to generate electron–hole pairs, which is a result of the fact that H-TiO<sub>2</sub> nanobelts have a more negative potential of conduction band (CB) and valence band (VB) than that of MoS<sub>2</sub> nanosheet.<sup>6</sup> Therefore, the photogenerated electrons in the H-TiO<sub>2</sub> surface can be easily transferred to the surface of the MoS<sub>2</sub> by the built-in potential in the heterojunction, leaving holes on the surface. Meanwhile, the holes left in the VB of the TiO<sub>2</sub> nanosheets and those transferred from the VB of TiO<sub>2</sub> can be consumed by the pollutants.<sup>4</sup> Some of the electrons approaching the edge of MoS<sub>2</sub> directly react with O<sub>2</sub> to produce ·O<sub>2</sub><sup>-</sup> under the co-catalytic activities of unsaturated active S atoms, which can accept electrons and act as active sites for TC degradation. Other unreacted electrons on the MoS<sub>2</sub> basal planes can be transferred to the CDs energy level and then can react with the target pollutant.<sup>29,39–43</sup> In view of this, the mechanism of an efficient multi-step electrons transfer process was proposed: (1) when the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> nanocomposite is suspended in aqueous captured solar illumination, H-TiO<sub>2</sub> simultaneously generates photoelectrons and holes; (2) the photogenerated electrons can be easily transferred to the MoS<sub>2</sub> layer from the conduction band (CB) of H-TiO<sub>2</sub>; (3) the

formation of a heterojunction between MoS<sub>2</sub> and the CDs bring about the further transfer of photoelectrons from MoS<sub>2</sub> to CDs. And above all, the relative band alignment of H-TiO<sub>2</sub>, MoS<sub>2</sub>, and CDs makes it feasible for migration of the photoexcited electrons through the vectorial electron transfer of H-TiO<sub>2</sub> → MoS<sub>2</sub> nanosheets → CDs layer. This process greatly inhibits the recombination of electron–hole pairs. Eventually, the accumulated electrons on the surface CD layer can capture and reduce the oxygen to form the reactive ·O<sub>2</sub><sup>-</sup>, which is a powerful oxidizing species responsible for degradation of the target pollutant. Meanwhile, the holes on the surface of H-TiO<sub>2</sub> can also react with H<sub>2</sub>O to generate ·OH. Therefore, the synergetic catalytic effect through the interfacial modulation and design of the charge-transfer channels by use of the integration of MoS<sub>2</sub> nanosheets and the CD layer plays a crucial role in the photocatalytic degradation.

## 4. Conclusion

In summary, a novel and stable carbon dots/MoS<sub>2</sub> few-layer nanosheet-coated hydrogenated TiO<sub>2</sub> nanobelt heterostructured catalyst was successfully synthesized by a facile process. Through optimizing the proportion of each component proportion, the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> catalysts showed the highest photodegradation activity when the content of the CDs/MoS<sub>2</sub> co-catalyst is 5.0 wt% and the mass ratio of MoS<sub>2</sub> to CDs was 4 : 1. The enhancement of the photocatalytic activity was mainly attributed to the mutual-benefit cooperation from the following three aspects: (1) the synergistic effect effectively suppresses the recombination of photogenerated electrons and holes; (2) the cooperative contribution of nano-sized CDs/MoS<sub>2</sub> few-layer sheets have more active edges and provide an excellent up-converted PL effect; (3) the CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> 3D hierarchical structure provides a favourable electron transfer pathway, H-TiO<sub>2</sub> → MoS<sub>2</sub> → CDs, for the efficient separation of electron–hole pairs. This kind of ternary CDs/MoS<sub>2</sub>@H-TiO<sub>2</sub> composite achieved a remarkable photocatalytic activity and demonstrated remarkable electron transport capabilities. Therefore, the findings from this research not only involved a systematic study of electron transfer, but also can be easily extended to the preparation of other CDs/MoS<sub>2</sub>-based 3D catalysts for a broad range of applications, such as solar cells, fuel cells, etc.

## Acknowledgements

We would like to acknowledge the Innovation Program Foundation of Jiangsu Province (SJLX15-0502), National Natural Science Foundation of China (21546006) and Six Talents Peaks Project in Jiangsu Province (XNY-009) and the Foundation Research Project of Jiangsu Province (the Natural Science Fund BK20150536).

## References

- 1 M. Yan, Y. Q. Hua, F. F. Zhu, W. Gu, J. H. Jiang, H. Q. Shen and W. D. Shi, *Appl. Catal., B*, 2017, **202**, 518–527.



- 2 N. Zhang, M. Q. Yang, S. Q. Liu, Y. G. Sun and Y. J. Xu, *Chem. Rev.*, 2015, **115**, 10307–10377.
- 3 C. T. Dinh, H. Yen, F. Kleitz and T. O. Do, *Angew. Chem., Int. Ed.*, 2014, **53**, 6618–6623.
- 4 W. J. Zhou, Z. Y. Yin, Y. P. Du, X. Huang, Z. Y. Zeng, Z. X. Fan, H. Liu, J. Y. Wang and H. Zhang, *Small*, 2013, **9**, 140–147.
- 5 S. J. Zhuo, M. W. Shao and S. T. Lee, *ACS Nano*, 2012, **6**, 1059–1064.
- 6 Q. J. Xiang, J. G. Yu and M. Jaroniec, *J. Am. Chem. Soc.*, 2012, **134**, 6575–6578.
- 7 Z. Zheng, B. B. Huang, X. D. Meng, J. P. Wang, S. Y. Wang, Z. Z. Lou, Z. Y. Wang, X. Y. Qin, X. Y. Zhang and Y. Dai, *Chem. Commun.*, 2013, **49**, 868–870.
- 8 J. Chen, W. X. Song, H. S. Hou, Y. Zhang, M. J. Jing, X. N. Jia and X. B. Ji, *Adv. Funct. Mater.*, 2015, **25**, 6793–6801.
- 9 Y. H. Lin, H. T. Hsueh, C. W. Chang and H. Chu, *Appl. Catal., B*, 2016, **199**, 1–10.
- 10 S. N. Phattalung, S. Limpijumnong and J. J. Yu, *Appl. Catal., B*, 2017, **200**, 1–9.
- 11 H. Zhang, L. H. Guo, D. B. Wang, L. X. Zhao and B. Wan, *ACS Appl. Mater. Interfaces*, 2015, **7**, 1816–1823.
- 12 J. Tian, Y. H. Leng, Z. H. Zhao, Y. Xia, Y. H. Sang, P. Hao, J. Zhan, M. C. Li and H. Liu, *Nano Energy*, 2015, **11**, 419–427.
- 13 Z. Bian, J. Zhu, S. Wang, Y. Cao, X. Qian and H. Li, *J. Phys. Chem. C*, 2008, **112**, 6258–6262.
- 14 R. Asahi, T. Morikawa, T. Ohwaki, K. Aoki and Y. Taga, *Science*, 2001, **293**, 269–271.
- 15 J. Wang, P. Zhang, X. Li, J. Zhu and H. Li, *Appl. Catal., B*, 2013, **134**, 198–204.
- 16 S. M. El-Sheikh, G. Zhang, H. M. El-Hosainy, A. A. Ismail, K. E. O'Shea, P. Falaras, A. G. Kontos and D. D. Dionysiou, *J. Hazard. Mater.*, 2014, **280**, 723–733.
- 17 Y. H. Lin, S. H. Chou and H. Chu, *J. Nanopart. Res.*, 2014, **16**, 1–12.
- 18 Z. Wang, X. Liu, W. Li, H. Wang and H. Li, *Ceram. Int.*, 2014, **40**, 8863–8867.
- 19 X. Chen, L. Liu, P. Y. Yu and S. S. Mao, *Science*, 2011, **331**, 746–750.
- 20 J. Zheng, L. Liu, G. B. Ji, Q. F. Yang, L. R. Zheng and J. Zhang, *ACS Appl. Mater. Interfaces*, 2016, **8**, 20074–20081.
- 21 T. Xia, C. Zhang, N. A. Oyler and X. Chen, *Adv. Mater.*, 2013, **25**, 6905–6910.
- 22 Y. H. Hu, *Angew. Chem., Int. Ed.*, 2012, **51**, 12410–12412.
- 23 A. K. Geim and I. V. Grigorieva, Van Der Waals Heterostructures, *Nature*, 2013, **499**, 419–425.
- 24 J. J. Duan, S. Chen, M. Jaroniec and S. Z. Qiao, *ACS Nano*, 2015, **9**, 931–940.
- 25 B. R. Sathe, X. Zou and T. Asefa, *Catal. Sci. Technol.*, 2014, **4**, 2023–2030.
- 26 H. Wang, Z. Lu, D. Kong, J. Sun, T. M. Hymel and Y. Cui, *ACS Nano*, 2014, **8**, 4940–4947.
- 27 K. Chang, Z. W. Mei, T. Wang, Q. Kang, S. Ouyang and J. H. Ye, *ACS Nano*, 2014, **8**, 7078–7087.
- 28 J. S. Wei, H. Ding, P. Zhang, Y. F. Song, J. Chen, Y. G. Wang and H. M. Xiong, *Small*, 2016, **12**, 5927–5934.
- 29 J. B. Chen, H. N. Che, K. Huang, C. B. Liu and W. D. Shi, *Appl. Catal., B*, 2016, **192**, 134–144.
- 30 J. Liu, Y. Liu, N. Y. Liu, Y. Z. Han, X. Zhang, H. Huang, Y. Lifshitz, S. T. Lee, J. Zhou and Z. H. Kang, *Science*, 2015, **347**, 970–974.
- 31 H. C. Zhang, H. Huang, H. Ming, H. T. Li, L. L. Zhang, Y. Liu and Z. H. Kang, *J. Mater. Chem.*, 2012, **22**, 10501–10506.
- 32 J. G. Hou, H. J. Cheng and Y. Chao, *Nano Energy*, 2015, **18**, 143–153.
- 33 S. J. Zhou, Q. N. Meng, L. Wang, J. H. Zhang, Y. B. Song, H. Jin, K. Zhang, H. C. Sun, H. Y. Wang and B. Yang, *Angew. Chem., Int. Ed.*, 2013, **52**, 3953–3957.
- 34 L. M. Xu, L. F. Ming and F. Chen, *ChemCatChem*, 2015, **7**, 1797–1800.
- 35 J. Di, J. X. Xia, Y. P. Ge, H. P. Li, H. Y. Ji, H. Xu, Q. Zhang, H. M. Li and M. N. Li, *Appl. Catal., B*, 2015, **168–169**, 51–61.
- 36 S. J. Yu, Y. H. Kim, S. Y. Lee, H. D. Song and J. H. Yi, *Angew. Chem., Int. Ed.*, 2014, **53**, 11203–11207.
- 37 Y. H. Sang, Z. H. Zhao, M. W. Zhao, P. Hao, Y. H. Leng and H. Liu, *Adv. Mater.*, 2014, **27**, 363–369.
- 38 F. Deng, K. Li, X. B. Luo, S. L. Luo, G. S. Zeng, S. L. Wu and C. T. Au, *Sci. Adv. Mater.*, 2014, **6**, 363–369.
- 39 J. G. Hong, H. J. Cheng, O. Takeda and H. M. Zhu, *Angew. Chem., Int. Ed.*, 2015, **54**, 8480–8484.
- 40 J. Di, J. X. Xia, M. Ji, B. Wang, S. Yin, Q. Zhang, Z. G. Chen and H. M. Li, *ACS Appl. Mater. Interfaces*, 2015, **7**, 20111–20123.
- 41 J. Liu, H. C. Zhang, D. Tang, X. Zhang, L. K. Yan, Y. Z. Han, H. Huang, Y. Liu and Z. H. Kang, *ChemCatChem*, 2014, 1–9.
- 42 H. Zhang, L. X. Zhao, F. L. Geng, L. H. Guo, B. Wan and Y. Yang, *Appl. Catal., B*, 2016, **180**, 656–662.
- 43 J. Di, J. X. Xia, M. X. Ji, H. P. Li, H. Xu, H. M. Li and R. Chen, *Nanoscale*, 2015, **7**, 11433–11443.

