


 Cite this: *RSC Adv.*, 2018, **8**, 11764

Morphology- and pH-dependent peroxidase mimetic activity of nanoceria†

 Xiaoshu Wei, Xiaofeng Li, Yuqian Feng and Sen Yang *

The peroxidase mimetic properties of nanoceria have attracted extensive attention in recent years. In this work, the peroxidase mimetic properties of CeO_2 nanocrystals with different morphologies, namely, nanocubes and nanorods, were investigated. Two types of oxidative species, HO^\cdot radicals and peroxide-like intermediates, were identified in the $\text{CeO}_2/\text{H}_2\text{O}_2$ systems. The formation of these oxidative species is strongly dependent on the pH value and the morphology of the CeO_2 nanocrystals. The origin of the peroxidase mimetic activity of nanoceria was mainly ascribed to the presence of HO^\cdot under acidic conditions, whereas the peroxide-like species also played a major role under neutral and basic conditions. CeO_2 nanorods with excellent redox properties and higher concentration of Ce^{3+} and oxygen vacancies were more favorable for the generation of both HO^\cdot and peroxide-like intermediates than that of CeO_2 nanocubes, exhibiting excellent peroxidase mimetic activity toward 2,2'-azino-bis(3-ethylbenzothiazoline-6-sulfonic acid) (ABTS), methylene blue (MB), and congo red (CR) in the presence of H_2O_2 .

Received 21st January 2018

Accepted 21st March 2018

DOI: 10.1039/c8ra00622a

rsc.li/rsc-advances

1 Introduction

Nanoceria has been extensively used in the field of catalysis because of the facile redox cycles between Ce^{3+} and Ce^{4+} .^{1–3} Among various catalytic applications of nanoceria, one interesting phenomenon is the peroxidase mimetic behavior, that is, some active oxidative species can be generated and some substrates can be oxidized concurrently during the catalytic decomposition of H_2O_2 .^{4–6} For example, it has been reported that CeO_2 nanoparticles exhibited excellent catalytic oxidation activity towards the classical peroxidase substrate 3,3,5,5-tetramethylbiphenyl dihydrochloride in the presence of H_2O_2 .⁷ Because of their peroxidase mimetic properties, nanoceria and cerium-containing materials have been widely used in medical diagnosis, biosensing, and Fenton-like processes for the degradation of organic pollutants.^{8–11}

Several oxidative species have been detected or proposed during the catalytic decomposition of H_2O_2 by nanoceria.^{5,12,13} Liu *et al.*⁸ attributed the peroxidase mimetic activity of $\text{H}_2\text{TCPP}-\text{CeO}_2$ nanocomposites to the formation of HO^\cdot , which was confirmed with a fluorescent probe technique. Lousada *et al.*¹⁴ confirmed the formation of HO^\cdot and studied the dynamics of formation of HO^\cdot . Besides HO^\cdot , the generation of other oxygen-derived free radicals such as HO_2^\cdot , O_2^\cdot , and O_2^- have also been suggested.^{15,16} However, several researchers have attributed the

oxidation ability of nanoceria to some brown peroxide-like intermediates,^{17–20} which oxidize organic substances through intermolecular rearrangement.^{17,21,22} Although the exact structure of the active oxidative species responsible for the peroxidase mimetic activity of nanoceria have not been fully elucidated, it is believed that the pH value of the reaction medium has a significant influence on the peroxidase mimetic properties of nanoceria.⁸ Most studies have shown that nanoceria could be used as a peroxidase mimic in the pH range of 2.0–6.0,^{7,23} whereas a few studies have shown that the peroxidase mimetic activity of nanoceria could be observed at even higher pH values.^{13,21} Therefore, further study is still needed to understand the relationship between the pH of the solution and the nature of the oxidative species and their oxidation abilities.

The peroxidase mimetic property of nanoceria originates from the redox cycles between Ce^{3+} and Ce^{4+} .^{15,24} Generally, the easier the redox cycles between Ce^{3+} and Ce^{4+} , the better the peroxidase mimetic activity of nanoceria.¹² Up to now, several strategies including doping ceria with heteroatom ions such as Zr^{4+} and decreasing the particle size of the ceria particles has been used to enhance the peroxidase mimetic activity of ceria.^{12,17,23} Zhou *et al.* reported that the redox performance of nanoceria could also be optimized by tuning the crystal planes exposed on the surfaces.²⁵ Since then, a series of studies have been carried out to optimize the catalytic performance of nanoceria for various reactions by tuning the morphology of CeO_2 nanocrystals.^{26–29} However, to the best of our knowledge, the influence of the exposed crystal facet on the peroxidase mimetic activity of nanoceria has only been reported in a recent paper, which found that the Fenton-like reactivity of CeO_2

Beijing Key Laboratory of Farmland Soil Pollution Prevention and Remediation, College of Resources and Environmental Sciences, China Agricultural University, Beijing 100193, PR China. E-mail: syang@cau.edu.cn; Tel: +86 1062733470

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8ra00622a



nanocrystal was related to their exposed facets.³⁰ Therefore, it is worth applying nanoceria with different morphologies as peroxidase mimetics to optimize the catalytic activity and understand the underlying mechanisms of the nanoceria mimic enzyme.

In this work, CeO_2 nanocubes and nanorods were prepared by a hydrothermal method and their peroxidase mimetic properties were investigated under both acidic and basic conditions. Our studies revealed a strong morphology-dependent peroxidase mimetic activity of nanoceria. The nature of the active oxidative species at different pH values and their oxidation abilities were investigated to gain a deep understanding of the mechanism of the peroxidase-mimetic activity of nanoceria.

2 Experiments

2.1 Materials

$\text{Ce}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$, NaOH , HCl , H_2O_2 (30%, w/w), *n*-butyl alcohol, methylene blue (MB) and congo red (CR) were purchased from Sinopharm Chemical Reagent Co. Ltd (Shanghai, China). Catalase, 2,2'-azino-bis(3-ethylbenzothiazoline-6-sulfonic acid) (ABTS) and 5,5-dimethyl-1-pyrroline *N*-oxide (DMPO) were obtained from Sigma-Aldrich Co. LLC. (Saint Louis, USA). All reagents were of analytical reagent grade and were used without further purification.

2.2 Synthesis of CeO_2 nanocubes and CeO_2 nanorods

CeO_2 nanocatalysts were synthesized through a hydrothermal process.^{25,31} Typically, $\text{Ce}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$ (1.5 g) was dissolved in distilled water, and an appropriate amount of 10% NaOH solution was rapidly added to give a final NaOH concentration of approximately 2.0 M. After stirring for approximately 15 min, the slurry (approximately 40 mL) was placed into a 50 mL Teflon-sealed autoclave and heated. The morphology of the as-prepared nanoceria depended on the hydrothermal temperature and reaction time, that is, nanocubes were formed by heating at 180 °C for 24 h and nanorods were formed by heating at 120 °C for 12 h. After cooling, the final product was collected by filtration, washed with deionized water, and then dried at 60 °C.

2.3 Catalyst characterization

The size and morphology of the nanoceria was characterized with a JEM-2100F high-resolution transmission electron microscope (HRTEM, JEOL, Japan). The powder X-ray diffraction (XRD) patterns were obtained on an D8 Advance X-ray diffractometer (Bruker, Germany) with Ni-filtered $\text{Cu K}\alpha$ radiation ($\lambda = 0.1541$ nm). The Brunauer-Emmett-Teller (BET) surface area was evaluated from nitrogen adsorption-desorption data recorded at 77 K using a model NOVA 3200e automated gas sorption system (Quantachrome, USA). X-ray photoelectron spectra (XPS) measurements were performed on an ESCALAB 250Xi high-performance electron spectrometer (Thermo Fisher, USA) using monochromatized $\text{Al K}\alpha$ ($h\nu = 1486.6$ eV) as the excitation source. Raman spectra were

collected by a Raman spectrometer (Renishaw inVia, UK) with a laser wavelength of 514.5 nm. Hydrogen temperature-programmed reduction (H_2 -TPR) was conducted with a Chemi-Sorb 2750 apparatus (Micromeritics, USA) equipped with a TCD detector. TPR was performed by heating the nanoceria samples (50 mg) at 10 °C min⁻¹ from 50–700 °C in a 5 vol% $\text{H}_2\text{-N}_2$ mixture with a flow rate of 25 mL min⁻¹.

2.4 Electron paramagnetic resonance (EPR) measurements

To monitor the potential radicals formed in the nanoceria/ H_2O_2 system, DMPO was used as the spin trap and EPR spectra were recorded using a JES-FA200 EPR spectrometer (X-band) with dual cavities (JEOL, Japan). Typical parameters were as follows: modulation frequency, 100 kHz; microwave frequency, 9.05 GHz; sweep width, 50 G; EPR microwave power, 3 mW; modulation amplitude, 1 G; time constant, 0.03 s; and sweep time, 2 min.

2.5 Peroxidase mimetics activity of nanoceria

The catalytic reaction was performed at 25 °C using 1 g L⁻¹ CeO_2 with 2 mM ABTS, 15 mg L⁻¹ MB or 70 mg L⁻¹ CR as substrate and 20 mM H_2O_2 , unless otherwise stated. Generally, catalyst powder was added into a conical flask containing an aqueous solution of the substrate. Then, a H_2O_2 solution was added to initiate the oxidation reaction. To avoid the influence of ions on the nanoceria activity, ultrapure water was used in the test, and the initial pH of the reaction system was adjusted using 0.1 M HCl and 0.1 M NaOH solution. The concentration of organics and H_2O_2 in supernatant was analyzed by using a UV-vis spectrophotometer (Beijing Purkinje General, China). The maximum wavelengths (λ_{max}) of H_2O_2 , ABTS⁺, MB and CR are 240, 734, 664 and 497 nm, respectively.

3 Results and discussion

3.1 Characterization of CeO_2 nanocubes and nanorods

The morphologies of the as-prepared samples were examined by transmission electron microscopy (TEM). The CeO_2 nanocubes had uniform cubic shapes with a size of 20–30 nm (Fig. 1a). The HRTEM image in Fig. 1b shows an interplanar spacing of 0.27 nm, corresponding to the (200) lattice fringe of CeO_2 , which indicates that the nanocubes were mainly enclosed by the (100) facets.³¹ As shown in Fig. 1c, CeO_2 nanorods had diameters of approximately 15–20 nm and lengths of 100–200 nm. The HRTEM analysis (Fig. 1d) revealed that the nanorods were single-crystalline and their growth direction was (110). This was consistent with the previously reported results that nanorods expose their (110) and (100) facets.²⁵

The XRD patterns of the CeO_2 nanocubes and nanorods are shown in Fig. 2a. All the diffraction peaks of both samples can be indexed to the pure fluorite structure of CeO_2 (JCPDS 34-0394).²⁸ The sharper peaks of the nanocubes indicated their higher crystallinity and bigger crystallite size than those of the nanorods,²⁶ which was consistent with the TEM and HRTEM analysis. The specific surface areas of the nanocerias were measured by a nitrogen gas adsorption-desorption isotherm



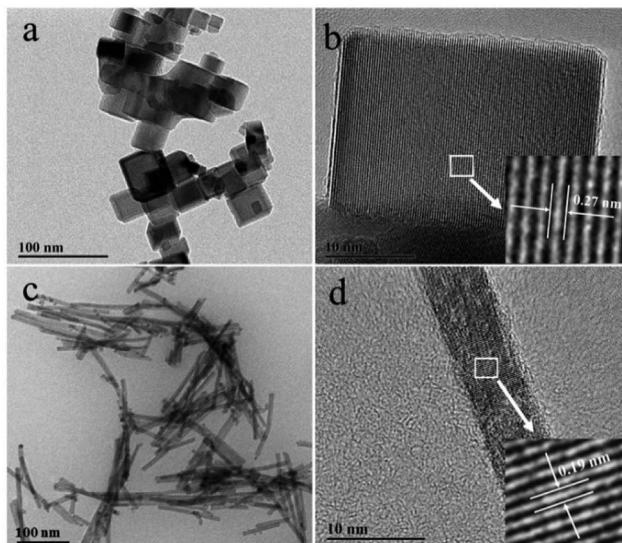


Fig. 1 TEM images of (a) CeO_2 nanocubes and (c) nanorods, and HRTEM images of (b) CeO_2 nanocubes and (d) nanorods.

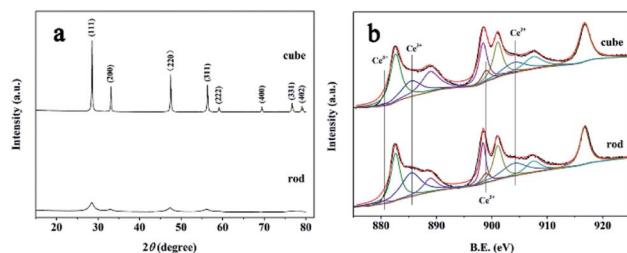


Fig. 2 XRD patterns (a) and Ce3d XPS spectra (b) of CeO_2 nanocubes and nanorods.

and calculated by the BET method. The nanorods exhibited a larger specific surface area ($89.9 \text{ m}^2 \text{ g}^{-1}$) than that of the nanocubes ($39.7 \text{ m}^2 \text{ g}^{-1}$).

The valence state of the Ce ions in the nanocerias was determined by XPS and the results are shown in Fig. 2b. The Ce3d XPS spectra revealed that a mixed valence state (Ce^{3+} and Ce^{4+}) was present and most of the Ce ions were Ce^{4+} in both nanoceria samples.³² However, the peaks attributed to Ce^{3+} in the nanorods, were clearly stronger than those for the nanocubes, as marked in Fig. 2b, indicating that more Ce^{3+} was on the surface of the nanorods.^{33,34} The Ce3d spectra were fitted using PeakFit software to calculate the Ce^{3+} concentration on the surface of both samples. The relative concentration of Ce^{3+} on the surface of the nanorods was 34.7%, which was much larger than that of the nanocubes (23.3%). The presence of more Ce^{3+} indicated that there were more oxygen vacancies in the CeO_2 nanorods, which was further verified by Raman analysis.

Fig. 3a displays the Raman spectra of the samples; two bands were observed for both samples. The presence of the prominent F_{2g} vibrational mode band at approximately 460 cm^{-1} was ascribed to the symmetric mode of the oxygen atoms around the cerium ions.²⁸ Compared with that of CeO_2 nanorods, the Raman band of the nanocubes displayed a clear increase in

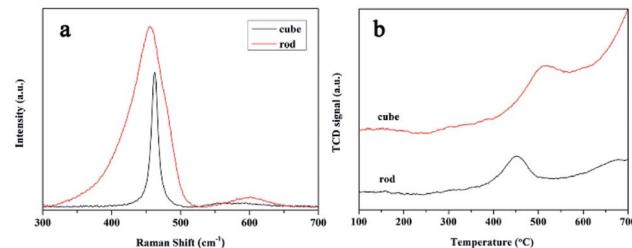


Fig. 3 (a) Raman spectra and (b) H_2 -TPR profiles of CeO_2 nanocubes and nanorods.

symmetry and a decrease in the full width at half maximum, along with an evident shift towards higher wave numbers. This was attributed to the higher degree of crystallinity and larger crystallite size of the nanocubes.^{35,36} The weak band at approximately 590 cm^{-1} was associated to the defect-induced mode (D).³⁵ The degree of defect sites on CeO_2 was estimated using the relative intensity of D/F_{2g} .^{28,36} The D/F_{2g} ratio of the CeO_2 nanorods was 0.056, which was higher than that of the nanocubes (0.023). This implied that CeO_2 nanorods had more defect sites such as oxygen vacancies, which was consistent with the XPS results.

The presence of more Ce^{3+} and defects in CeO_2 nanorods suggested that the nanorods could be more reducible than the nanocubes. Subsequently, the redox properties of the nanoceria samples were examined by H_2 -TPR. The TPR profiles (Fig. 3b) of both samples showed two reduction bands, one located below $580 \text{ }^\circ\text{C}$ and one above $600 \text{ }^\circ\text{C}$. The low-temperature reduction band is related to the surface oxygen reduction and is of particular interest in catalytic reactions.³² The low-temperature peak position of the CeO_2 nanorods was at $450 \text{ }^\circ\text{C}$, which was much lower than that of the nanocubes ($510 \text{ }^\circ\text{C}$), indicating that the CeO_2 nanorods were much more reducible than the nanocubes.²⁸ The facile redox performance of the CeO_2 nanorods indicated that the CeO_2 nanorods should perform well as peroxidase mimetics.

3.2 H_2O_2 decomposition and probing the possible oxidative species

The decomposition of H_2O_2 over CeO_2 nanocubes and nanorods was first investigated from pH 3.0 to 9.0. This set of data is for 20 mM H_2O_2 in the presence of 1 g L^{-1} CeO_2 at $25 \text{ }^\circ\text{C}$. Fig. 4a shows the H_2O_2 concentration changes as a function of time. The decomposition of H_2O_2 in the presence of CeO_2 follows first-order kinetics as previously reported (Fig. S1†).^{14,37} The rate coefficients are given in Table S1.† It is clear that the effect of the pH on the decomposition of H_2O_2 over nanoceria is not obvious and only a slight increase in conversion can be observed with increasing pH from 3.0 to 9.0.³⁸ However, CeO_2 nanorods display higher activity over all reactivity towards H_2O_2 . When the amount of eliminated H_2O_2 was normalized to the surface area of nanocubes and nanorods, CeO_2 nanorods still possessed higher level of activity (Fig. 4b).

It has been reported that nanoceria could facilitate the decomposition of H_2O_2 to produce HO^\cdot through a series of reactions analogous to Fenton/Haber Weiss reactions:^{15,39,40}




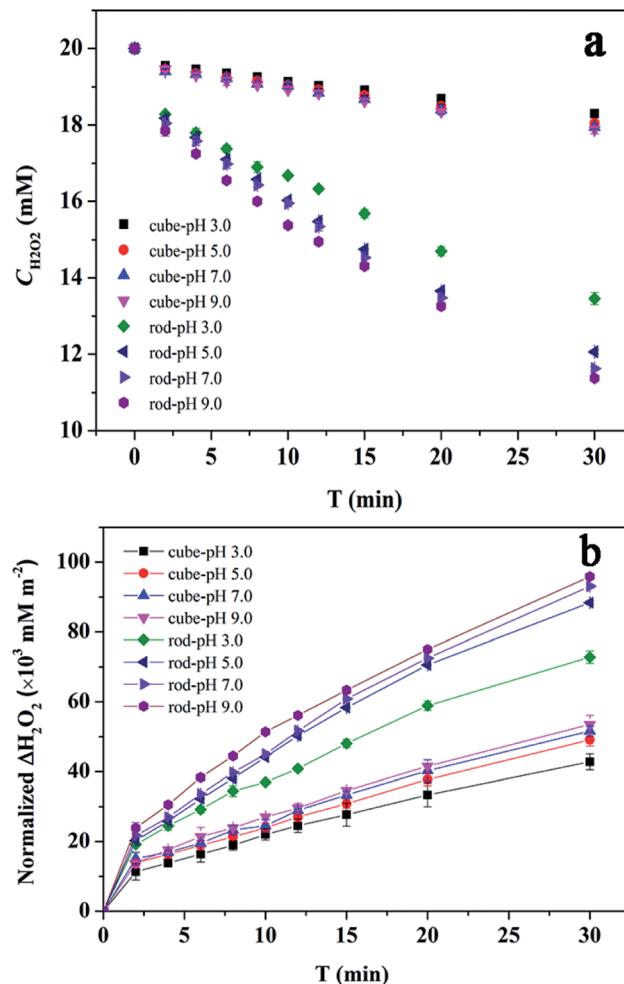


Fig. 4 Catalytic activity of CeO₂: (a) concentration changes of H₂O₂ as a function of reaction time and (b) the eliminated H₂O₂ was normalized to CeO₂ surface area (20 mM H₂O₂, 1 g L⁻¹ CeO₂, 25 °C).



To probe the possible generation of HO[·] during the catalytic decomposition of H₂O₂ over nanoceria, EPR was performed using the DMPO as a spin trap. As shown in Fig. 5, a 4-line EPR spectrum characteristic of DMPO-OH adducts was detected for a suspension of nanorods upon the addition of H₂O₂, but the intensity of the DMPO-OH signal decreased from pH 3.0 to pH 9.0. Similar results were obtained for a suspension of nanocubes, except the intensity of the DMPO-OH peaks was significantly lower than those of the nanorods under the same conditions. These results clearly show that HO[·] can be generated in the catalytic decomposition of H₂O₂ and the yield of HO[·] is decreased with increasing pH from 3.0 to 9.0.^{22,41} And CeO₂ nanorods with better redox properties were more favorable for the generation of HO[·] than their nanocube counterparts. Then the ability of the nanoceria to generate HO[·] strongly depends on its redox properties.⁴⁰

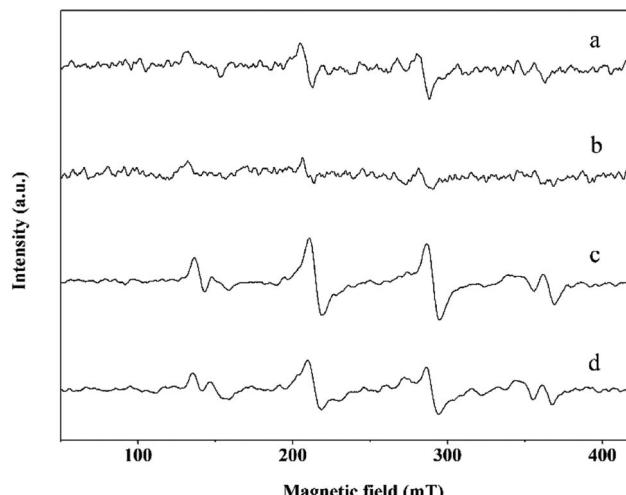


Fig. 5 DMPO spin trapping EPR spectra of CeO₂/H₂O₂ system. Nanocubes/H₂O₂ at pH 3.0 (a) and 9.0 (b); nanorods/H₂O₂ at pH 3.0 (c) and 9.0 (d). The incubation time is 2 min, and [CeO₂] = 1 g L⁻¹, [H₂O₂] = 20 mM.

It should be noted that a rapid color change was observed upon the addition of H₂O₂ into the nanoceria suspensions: the nanocubes suspension became light yellow and the nanorods suspension became deep yellow (Fig. 6). The color change was attributed to the formation of another type of oxidative species (the peroxide-like intermediates) from the reaction between H₂O₂ and CeO₂.^{12,19,38} The small variations in the color change of nanoceria from pH 3.0 to 9.0 were almost completely imperceptible to the eye, indicating that the formation of peroxide-like intermediates was independent of the pH value. Compared with the suspension of the nanocubes/H₂O₂, the deeper color of the nanorods/H₂O₂ system indicated more

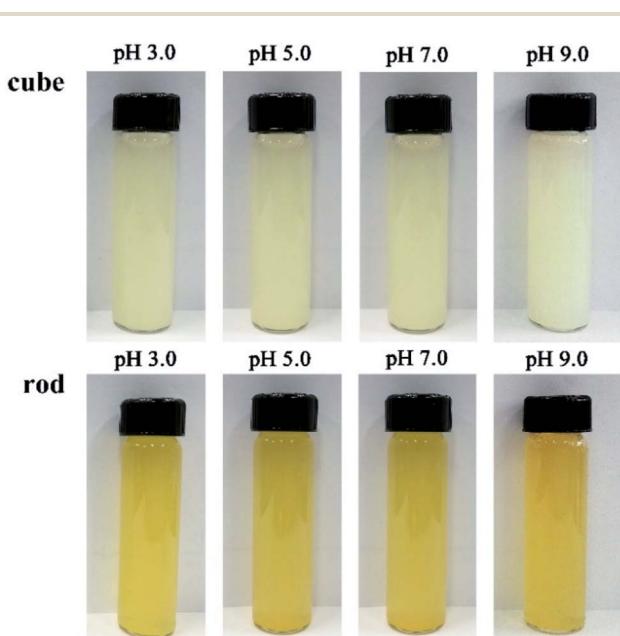


Fig. 6 Photographs of nanoceria suspensions after the addition of H₂O₂ at various pH (50 mM H₂O₂, 0.5 g L⁻¹ CeO₂).

peroxide-like species were generated owing to the presence of more Ce^{3+} and oxygen vacancies, as proved by XPS and Raman analysis. A generally accepted view is that the ease of $\text{Ce}^{3+}/\text{Ce}^{4+}$ redox cycles plays a significant role in the decomposition of H_2O_2 and the generation of peroxide-like intermediates.²¹ In this process, the rate of Ce^{3+} oxidation is much faster than that of Ce^{4+} reduction, and high concentration of Ce^{3+} would enhance the reducibility of ceria.^{32,38,42} Therefore, high peroxidase mimetic activity of ceria nanorods can be attributed to the high concentration of Ce^{3+} and the better reducibility.

The above results show that there were two types of oxidative species, namely HO^\cdot and peroxide-like intermediates, which can be generated in the nanoceria/ H_2O_2 systems. The formation of these oxidative species was strongly dependent on the pH value and the morphology of the CeO_2 nanocrystals, which determined the peroxidase mimetic performance of nanoceria.

3.3 Peroxidase mimetic activity of CeO_2 nanocubes and nanorods

The peroxidase mimetic activity of the CeO_2 samples was evaluated semiquantitatively by the oxidation of ABTS in the presence of H_2O_2 from pH 3.0 to 9.0. ABTS is typically used as a horseradish peroxidase substrate, which develops a green color ($\text{ABTS}^\cdot+$) upon oxidation in aqueous solution. Control experiments showed that the color change of the systems was negligible without the presence of nanoceria or H_2O_2 (Fig. S2†). As shown in Fig. 7, a distinct and rapid change of the nanoceria/ H_2O_2 suspension to a green color was observed upon the addition of ABTS, indicating that nanoceria did exhibit high peroxidase-mimetic activity, as reported previously.^{7,10} Compared with the nanocubes, the nanorods exhibited a higher activity under the current conditions, which could be explained by the generation of more HO^\cdot and peroxide-like intermediates owing to their better redox property and high concentration of Ce^{3+} and oxygen vacancies. Moreover, it is evident that the color

of the suspensions changes from dark green to lighter with pH value from 3.0 to 9.0, showing a strong pH-dependent peroxidase mimetic activity of nanoceria. Nanoceria display higher peroxidase mimetic activity at acidic conditions and the time-dependent UV-vis spectra of the oxidized product of ABTS ($\text{ABTS}^\cdot+$) at room temperature are shown in Fig. 8. To further understand the peroxidase mimetic behaviors of the ceria nanocubes and nanorods, decolorization of MB and CR were carried out.

3.4 Decolorization of MB and CR in nanoceria/ H_2O_2 system

First, decolorization of 15 mg L^{-1} MB with 1.0 g L^{-1} nanoceria and 20 mM H_2O_2 at pH 3.0 was investigated. It turned out that the decolorization of MB over nanorods was 11.6% after 30 min, while only 4.8% was achieved over nanocubes. To investigate the role of HO^\cdot and peroxide-like intermediates in the decolorization process, we performed this experiment by adding 200 mM *n*-butanol as a radical scavenger before the reaction was initiated. Excess *n*-butanol in solution can scavenge all the HO^\cdot produced in the H_2O_2 decomposition process and inhibit the degradation of MB.⁴⁰ As expected, the decolorization of MB was completely inhibited in the presence of *n*-butanol. This result verified that the peroxidase mimetic activity of nanoceria was mainly owing to the formation of HO^\cdot under acidic conditions.^{13,14} It is well known that HO^\cdot exhibits high reactivity and can non-selectively oxidize most organic compounds at near diffusion-controlled rates under acidic condition.⁴³ Although the peroxide-like intermediates were also present, it seemed they did not work. In fact, Chen *et al.*⁴⁴ and Hamoud *et al.*¹² reported that the peroxide-like intermediates were prone to decompose into HO^\cdot under acidic conditions. This can be used to explain the complete inhibition decolorization of MB in the presence of *n*-butanol.

Subsequently, the decolorization of MB at pH 9.0 was carried out. Because of the strong adsorption on ceria arising under these conditions (pH 9.0), both adsorption and oxidative degradation contributed to the total decolorization. After

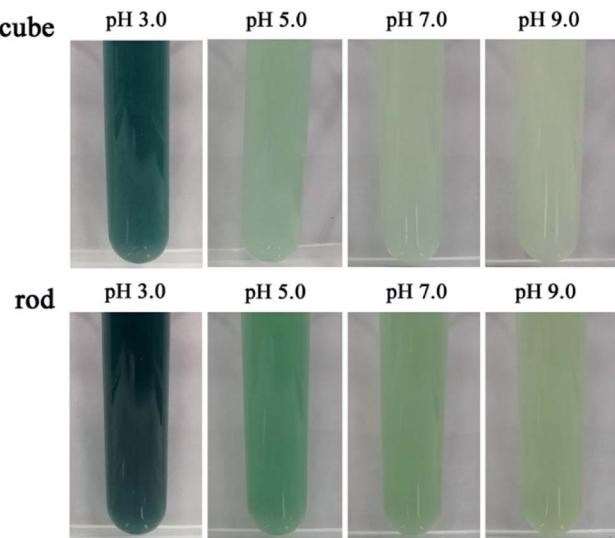


Fig. 7 The pH effect on the production of colored product owing to ABTS oxidation in the nanoceria/ H_2O_2 system (0.2 g L^{-1} CeO_2 , 10 mM H_2O_2 , 5 mM ABTS, t: 2 min).

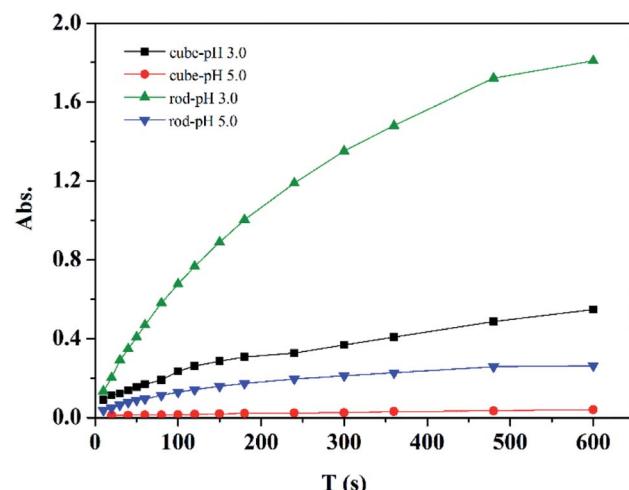


Fig. 8 Time-dependent absorbance changes at 734 nm of ABTS in different systems (0.1 g L^{-1} CeO_2 , 5 mM H_2O_2 and 2 mM ABTS).

eliminating the interference arising from adsorption, the degradation of MB was obtained (more information is provided in the ESI†). After 0.5 h, the degradation of MB in the presence of CeO_2 nanorods and nanocubes was only 5.3% and 3.4%, respectively. These results suggested that nanoceria/ H_2O_2 system could degrade MB at pH 9.0 but the peroxidase mimetic reactivity of nanoceria was much lower than that at pH 3.0. To further understand the peroxidase-mimetic activity of nanoceria under basic conditions, the degradation of CR, a typical anionic azodye, was investigated at pH 9.0. The CR (70 mg L^{-1}) could be completely degraded after 1 h in the presence of nanorods, whereas the degradation was only 8.2% in the presence of nanocubes. Interestingly, this time, the addition of *n*-butanol could not completely inhibit the degradation of both MB and CR under basic conditions, although the degradation rates of dye were decreased with a certain extent. For example, the complete degradation time of CR in nanorods/ H_2O_2 system was delayed from 1 h to 2.5 h upon addition of *n*-butanol. These results suggested that both HO^\cdot and the peroxide-like intermediates were acting as the oxidative species in the nanoceria/ H_2O_2 system under basic conditions.²⁹ According to previous reports, under neutral and basic conditions, the peroxide-like intermediates can directly function as peroxidase-like active sites^{23,45} or induce an intermolecular rearrangement to achieve the oxidation of organics.^{21,22} Because oxidation ability of HO^\cdot was much weaker under basic conditions than acidic conditions,^{12,46} the importance of the peroxide-like intermediates was raised.

4 Conclusions

Nanoceria possesses strong morphology- and pH-dependent peroxidase-like activity for the degradation of ABTS, MB and CR. Two types of oxidative species were generated in the nanoceria/ H_2O_2 systems, namely, HO^\cdot and peroxide-like intermediates. Under acidic conditions, HO^\cdot are primarily responsible for the peroxidase mimetic activity of nanoceria; under neutral and basic conditions, HO^\cdot and peroxide-like intermediates are responsible for activity. Compared with CeO_2 nanocubes, ceria nanorods exhibited a higher peroxidase activity owing to their excellent redox property and more Ce^{3+} and oxygen vacancies.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors are grateful for the financial support provided by the National Natural Science Foundation of China (Grant No. 21476251).

References

- 1 M. Tamura and K. Tomishige, *Angew. Chem., Int. Ed.*, 2015, **54**, 864.
- 2 T. Montini, M. Melchionna, M. Monai and P. Fornasiero, *Chem. Rev.*, 2016, **116**, 5987.
- 3 A. Trovarelli, *Catal. Rev.: Sci. Eng.*, 1996, **38**, 439.
- 4 M. Das, S. Patil, N. Bhargava, J. F. Kang, L. M. Riedel, S. Seal and J. J. Hickman, *Biomaterials*, 2007, **28**, 1918.
- 5 W. Lin, Y.-w. Huang, X.-D. Zhou and Y. Ma, *Int. J. Toxicol.*, 2006, **25**, 451.
- 6 C. Xu and X. G. Qu, *NPG Asia Mater.*, 2014, **6**, e90.
- 7 X. Jiao, H. J. Song, H. H. Zhao, W. Bai, L. C. Zhang and Y. Lv, *Anal. Methods*, 2012, **4**, 3261.
- 8 Q. Y. Liu, Y. Y. Ding, Y. T. Yang, L. Y. Zhang, L. F. Sun, P. P. Chen and C. Gao, *Mater. Sci. Eng., C*, 2016, **59**, 445–453.
- 9 X. M. Li, L. Sun, A. Q. Ge and Y. S. Guo, *Chem. Commun.*, 2011, **47**, 947.
- 10 L. F. Sun, Y. Y. Ding, Y. L. Jiang and Q. Y. Liu, *Sens. Actuators, B*, 2017, **239**, 848.
- 11 H. Issa Hamoud, G. Finqueneisel and B. Azambre, *J. Environ. Manage.*, 2017, **195**, 195.
- 12 H. I. Hamoud, B. Azambre and G. Finqueneisel, *J. Chem. Technol. Biotechnol.*, 2016, **91**, 2462.
- 13 E. Aneggi, V. Cabbai, A. Trovarelli and D. Goi, *Int. J. Photoenergy*, 2012, **2012**, 694721.
- 14 C. M. Lousada, M. Yang, K. Nilsson and M. Jonsson, *J. Mol. Catal. A: Chem.*, 2013, **379**, 178.
- 15 T. S. Wu, Y. Y. Zhou, R. F. Sabirianov, W. N. Mei, Y. L. Soo and C. L. Cheung, *Chem. Commun.*, 2016, **52**, 5003.
- 16 S. M. Hirst, A. S. Karakoti, R. D. Tyler, N. Sriranganathan, S. Seal and C. M. Reilly, *Small*, 2009, **5**, 2848.
- 17 W. D. Cai, F. Chen, X. X. Shen, L. J. Chen and J. L. Zhang, *Appl. Catal., B*, 2010, **101**, 160.
- 18 S. Y. Hao, J. Hou, P. Aprea and F. Pepe, *Appl. Catal., B*, 2014, **160**, 566.
- 19 F. H. Scholes, A. E. Hughes, S. G. Hardin, P. Lynch and P. R. Miller, *Chem. Mater.*, 2007, **19**, 2321.
- 20 E. Grulke, K. Reed, M. Beck, X. Huang, A. Cormack and S. Seal, *Environ. Sci.: Nano*, 2014, **1**, 429.
- 21 P. F. Ji, L. Z. Wang, F. Chen and J. L. Zhang, *ChemCatChem*, 2010, **2**, 1552.
- 22 F. Chen, X. X. Shen, Y. C. Wang and J. L. Zhang, *Appl. Catal., B*, 2012, **121**, 223.
- 23 Z. M. Tian, J. Li, Z. Y. Zhang, W. Gao, X. M. Zhou and Y. Q. Qu, *Biomaterials*, 2015, **59**, 116.
- 24 L. Artiglia, S. Agnoli, M. C. Paganini, M. Cattelan and G. Granozzi, *ACS Appl. Mater. Interfaces*, 2014, **6**, 20130.
- 25 K. B. Zhou, X. Wang, X. M. Sun, Q. Peng and Y. D. Li, *J. Catal.*, 2005, **229**, 206.
- 26 T. Naganuma, *Nano Res.*, 2017, **10**, 199.
- 27 L. Wang, G. Lu, D. Yang, J. Wang, Z. B. Zhu, Z. X. Wang and K. B. Zhou, *ChemCatChem*, 2013, **5**, 1308.
- 28 H. Y. Tan, J. Wang, S. Z. Yu and K. B. Zhou, *Environ. Sci. Technol.*, 2015, **49**, 8675.
- 29 T. S. Sreeremya, A. Krishnan, K. C. Remani, K. R. Patil, D. F. Brougham and S. Ghosh, *ACS Appl. Mater. Interfaces*, 2015, **7**, 8545.
- 30 C. Zang, X. Zhang, S. Hu and F. Chen, *Appl. Catal., B*, 2017, **216**, 106.



31 Z. Yang, K. Zhou, X. Liu, Q. Tian, D. Lu and S. Yang, *Nanotechnology*, 2007, **18**, 185606.

32 X. W. Liu, K. B. Zhou, L. Wang, B. Y. Wang and Y. D. Li, *J. Am. Chem. Soc.*, 2009, **131**, 3140.

33 D. Yang, L. Wang, Y. Z. Sun and K. B. Zhou, *J. Phys. Chem. C*, 2010, **114**, 8926.

34 Y. Xue, Q. F. Luan, D. Yang, X. Yao and K. B. Zhou, *J. Phys. Chem. C*, 2011, **115**, 4433.

35 J. E. Spanier, R. D. Robinson, F. Zheng, S. W. Chan and I. P. Herman, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2001, **64**, 245407.

36 W. H. Weber, K. C. Hass and J. R. McBride, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1993, **48**, 178.

37 A. Hiroki and J. A. LaVerne, *J. Phys. Chem. B*, 2005, **109**, 3364.

38 Y. J. Wang, H. Dong, G. M. Lyu, H. Y. Zhang, J. Ke, L. Q. Kang, J. L. Teng, L. D. Sun, R. Si, J. Zhang, Y. J. Liu, Y. W. Zhang, Y. H. Huang and C. H. Yan, *Nanoscale*, 2015, **7**, 13981.

39 E. G. Heckert, S. Seal and W. T. Self, *Environ. Sci. Technol.*, 2008, **42**, 5014.

40 L. J. Xu and J. L. Wang, *Environ. Sci. Technol.*, 2012, **46**, 10145.

41 P. Zhang, D. Sun, M. Wen, J. Yang, K. Zhou and Z. Wang, *Adv. Synth. Catal.*, 2012, **354**, 720.

42 R. N. McCormack, P. Mendez, S. Barkam, C. J. Neal, S. Das and S. Seal, *J. Phys. Chem. C*, 2014, **118**, 18992.

43 A. D. Bokare and W. Choi, *J. Hazard. Mater.*, 2014, **275**, 121.

44 Y. C. Wang, X. X. Shen and F. Chen, *J. Mol. Catal. A: Chem.*, 2014, **381**, 38.

45 H. Zhao, Y. M. Dong, P. P. Jiang, G. L. Wang and J. J. Zhang, *ACS Appl. Mater. Interfaces*, 2015, **7**, 6451.

46 S. H. Bossmann, E. Oliveros, S. Gob, S. Siegwart, E. P. Dahlen, L. Payawan, M. Straub, M. Worner and A. M. Braun, *J. Phys. Chem. A*, 1998, **102**, 5542.

