# **RSC Advances**



REVIEW

View Article Online

View Journal | View Issue



Cite this: RSC Adv., 2018, 8, 30125

# Recent advances in syntheses, properties and applications of TiO<sub>2</sub> nanostructures

Imran Ali, 10 \*ab Mohd Suhail, b Zied A. Alothman and Abdulrahman Alwarthan and Abdulrahman and Abdulr

TiO<sub>2</sub> is a compound of great importance due to its remarkable catalytic and distinctive semiconducting properties. It is also a chemically stable, non-toxic and biocompatible material. Nano TiO<sub>2</sub> is strong oxidizing agent with a large surface area and, hence, high photo-catalytic activities. With low production cost and a high dielectric constant, it is an inexpensive material. It can be prepared by diverse procedures such as solution and gas phase procedures. Nowadays, TiO<sub>2</sub> is being used frequently for photo degradation of organic molecules and water splitting for hydrogen generation. Most important applications include purification, disinfection of waste water, self-cleaning coatings for buildings in urban areas and the production of the green currency of energy (hydrogen) by splitting water. The review describes the advances in the syntheses, properties and applications of TiO<sub>2</sub> nano structures. Besides, efforts are also made to discuss the working mechanism and future challenges and perspectives.

Received 2nd August 2018 Accepted 20th August 2018

DOI: 10.1039/c8ra06517a

rsc.li/rsc-advances

# 1. Introduction

Nowadays, nano-structured materials are an important area of research owing to their several unique characteristic features. Among all the transition metal oxides, TiO2 nano-structures are the most attractive materials in modern science and technology. TiO<sub>2</sub> has been widely used commercially in doughnuts, cosmetics, pigments, 1 catalysts, sunscreens, 2,3 solar cells, 4 water splitting etc. TiO<sub>2</sub> is being used in plastics, paints, varnishes, papers, medicines, inks, medications, toothpaste, food products, and industries.5-10 In 1972 first of all, Fujishima and Honda4 reported photo-assisted water splitting under UV light on a TiO2 photo anode as a semiconductor.4,11,12 The diverse claims can be separated into "environmental" and "energy" groups, several of which depend on the TiO2 properties itself as well as on the changes of the TiO2 material host (e.g. with organic and inorganic dyes). In previous years, the research activity expansion has been observed in nanotechnology and nanoscience.13-17 On the modification, preparation and properties of nano-materials, a significant amount of research, reports and reviews have been published recently4,11-40 to know and précis the progress in this field. TiO2 nanostructures in various forms, among the unique characteristics of nanomaterials, are gaining broader applications due to their sizerelated characteristics. For nanometer scale TiO2 the energy structure becomes discrete due to its surface,

photochemical and photo physical properties. Consequently, several works have focused on nano crystalline TiO<sub>2</sub> syntheses with a high surface area. As a photocatalyst, <sup>15,16,27</sup> TiO<sub>2</sub> nanostructures have drawn much attention and are projected to show a significant role in serving to resolve several pollution and environmental problems. Thus, using TiO<sub>2</sub> for H<sub>2</sub> production and photo-assisted water splitting devices offers a way for hygienic and low price production of hydrogen by solar energy. <sup>13,41</sup>

This review aims to give an inclusive data on the advances in  ${\rm TiO_2}$  based nanostructure, recent investigation and the development efforts, which tack energy and environmental challenges in consideration. Besides, the crystal structure, optical, electrical/electronic and adsorption, surface area, porosity properties of  ${\rm TiO_2}$  nanostructure are discussed. The procedures of preparations, fabrications (nanoparticles, nanorods, nanowires, and nanotubes), the conditions of syntheses and accountability for regulation of titanate nanostructures morphology are also discussed.  ${\rm TiO_2}$  nanostructures applications in electrocatalysis, environment and energy challenges are also highlighted. Finally, the mechanism of action and future challenges are also highlighted.

# 2. Properties of TiO<sub>2</sub> nanostructures

### 2.1 Crystal structure of TiO<sub>2</sub>

Titanium dioxide [titanium(iv) oxide or titania] has a molecular formula  $TiO_2$  with 79.87 as molecular weight.  $TiO_2$ , a non-toxic material, chemically stable, biocompatible and strong oxidizing agent (with large surface area) has very high photocatalytic activity. It is an inexpensive material with high dielectric constant and low production cost.  $TiO_2$  crystal exists in three

<sup>&</sup>lt;sup>a</sup>Department of Chemistry, College of Sciences, Taibah University, Al-Medina Al-Munawara – 41477, Saudi Arabia. E-mail: drimran.chiral@gmail.com; drimran\_ali@yahoo.com

<sup>&</sup>lt;sup>b</sup>Department of Chemistry, Jamia Millia Islamia, Central University, New Delhi, India <sup>c</sup>Department of Chemistry, College of Science, King Saud University, Riyadh 11451, Kingdom of Saudi Arabia

**RSC Advances** 

common polymorphs in nature i.e. brookite, anatase, rutile, 42,43 and some few common structures of TiO2 II i.e. columbite,44 TiO<sub>2</sub> III: baddeleyite, 45,46 TiO<sub>2</sub> (R) (ramsdellite), 47 TiO<sub>2</sub> (B) (monoclinic)48 and TiO2 (H) (hollandite).49

Rutile is the most thermodynamically constant among the different polymorphs structures.<sup>50</sup> From 400 to 1200 °C, it's critical temperature can vary which depends on the grain impurities and size.51 The optical and electrical properties and crystal structural of rutile, brookite and anatase are given in Table 1.51-63 These are discussed in the following paragraphs.

### 2.2 Rutile

In a tetragonal structure, with 6 atoms per unit cell (Fig. 1), rutile is the most stable having TiO<sub>6</sub> octahedron showing a slight orthorhombic distortion. 64-66 Rutile phase is stable while at these conditions TiO2 converts thermodynamically into auspicious phase. 67 For unit sizes > 14 nm, rutile phase becomes more stable than anatase.68 Predominantly, the crystals of natural rutile exhibit (110) surface. 42 This surface is the most stable stoichiometric rutile surface.<sup>69</sup> In the unit cell of rutile, 4 oxygen atoms form a partial octahedron about Ti70 while 2 titanium atoms (at [0, 0, 0] and  $\left[\frac{1}{2}, \frac{1}{2}, \frac{1}{2}\right]$ ) positions, separately are available. Distinctly, octahedron is linked to 10 near octahedra, out of which 2 parts an edge and eight share a bend with it. The octahedral edge shared are aligned along [001] direction as shows in Fig. 1.70

### 2.3 Anatase

TiO<sub>6</sub> octahedron distortion is significantly large for anatase phase while TiO<sub>2</sub> has a tetragonal structure, hence, the symmetry of anatase is lower than orthorhombic (Fig. 1).70 The energy change between these 2 phases is minor closely ( $\sim$ 2 to 10 kJ mol<sup>-1</sup>).<sup>71</sup> At 0 K, the rutile phase is not more thermodynamically constant than anatase. The unit cells of anatase




Fig. 1 Crystal structures of the rutile and anatase phases of TiO<sub>2</sub>. Small spheres represent Ti atoms, large spheres represent oxygen atoms.

contain 4 titanium atoms (at  $\left[\frac{1}{2}, \frac{1}{2}, \frac{1}{2}\right]$ , [0, 0, 0],  $\left[-\frac{1}{2}, 0, -\frac{1}{4}\right]$ and  $\left[0, \frac{1}{2}, \frac{1}{4}\right]$ ) and 8 oxygen atoms, which form a partial TiO<sub>6</sub>

octahedron around Ti;70 with division of 4 edges of each octahedron.

### 2.4 Brookite

It is one of the 3 naturally occurring polymorphs of TiO<sub>2</sub>, which belongs to orthorhombic crystal system. It contains a larger cell volume with 8 TiO2 groups per unit cell (Fig. 2).53 Brookite is also the least dense form compared to anatase and rutile.65 Besides, it displays photocatalytic activity.72 Liu et al.73 investigated principled metal free photocatalytic water splitting. For this investigation the authors modified these surfaces by high pressure. Before and after modification, water splitting on usual anatase single crystal facets and on wafer slices of the [001] plane was investigated. Fig. 3 shows phase transition in TiO<sub>2</sub>

Table 1 Comparison of the crystal structural, optical and electrical properties for TiO<sub>2</sub> nanostructures

| Properties<br>Crystal structure<br>Lattice constant (Å)  | Rutile<br>Tetragonal<br>a = 4.5936<br>c = 2.9587 (ref. 312)                                      | Anatase<br>Tetragonal $a = 3.784$ $c = 9.515$ (ref. 312) | Brookite<br>Orthorhombic<br>a = 9.184<br>b = 5.447 (ref. 312) |
|--|--|--|---|
| Space group<br>Molecule (cell)   | P42/mnm <sup>52</sup>  | $I4_1/amd$   | c = 5.154<br>Pbca<br>4  |
| Volume/molecule (ų)<br>Density (g cm <sup>-3</sup> )   | 31.21 (ref. 54)<br>4.13  | 34.061<br>3.79   | 32.172<br>3.99  |
| Ti-O bond length (Å)   | 1.949 (4) <sup>53</sup><br>1.980 (2)   | 1.937 (4)<br>1.965 (2)                                   | 1.87-2.04   |
| O-Ti-O bond angle  | 81.2°<br>90.0°   | 77.7°<br>92.6°   | 77.0-105°   |
| Band gap at 10 K<br>Static dielectric constant ( $\varepsilon_0$ , in MHz range)   | 3.051 eV (ref. 54)<br>173 (ref. 314 and 315)   | 3.46 eV (ref. 313)<br>48 (ref. 55)                       |   |
| High frequency dielectric constant, $\varepsilon_{\infty}$ ( $\lambda = 600$ nm)<br>Nature of conductivity at room temperature (undoped) | 8.35 (ref. 56)<br>n-type semiconductor <sup>58–75</sup>  | 6.25 (ref. 57)   |   |
| Mott transition<br>Electron effective mass   | Not observed <sup>60</sup><br>9–13 m, <sup>61</sup> 10–30 m, <sup>62</sup> 12–32 m <sup>63</sup> | Observed <sup>313</sup> $\sim$ 1 m (ref. 313)            |   |




Fig. 2 Lattice structure of brookite TiO<sub>2</sub>.

with the change in pressure and temperature.<sup>74</sup> The temperature for transformation can be improved by accumulation impurities into TiO<sub>2</sub>. Anatase phase for powder samples containing V, Mo, & W respectively completely disappeared<sup>75</sup> at temperature about 530, 680, and 830 °C.

### 2.5 Optical properties of TiO<sub>2</sub>

In the range from IR to visible spectra, the rutile is more anisotropic than anatase. Contrarily, anatase shows important anisotropy in the band gap region.<sup>76</sup> At about 0.75 to 1.18 eV (ref. 77–80) for rutile, a blue color appearance dependent on the amount of reduction of TiO<sub>2</sub>, arises from the visible part infrared absorption band peaking. The blue color appearance in IR has also been observed in anatase too.<sup>81,82</sup> Besides, at 3.0 eV an oxygen vacancy causing a yellow color is a color center.<sup>81</sup>

### 2.6 Electrical/electronic properties of TiO<sub>2</sub>

The electrical/electronic properties of  ${\rm TiO_2}$  nanostructures are dependent on the crystallographic directions. Titanium dioxide nanostructure (titania) is an important photocatalytic material, which exists in to 2 chief polymorphs *i.e.* rutile and anatase with tetragonal coordinations. Table 1 shows the several  ${\rm TiO_2}$  electrical properties. A semiconductor,  ${\rm TiO_2}$  has high resistivity ( $\sim 10^{15}~\Omega$  cm),  $^{83}$  titanium interstitials and bulk oxygen vacancies. These are considered to generate low electron donor levels that donate to the electric conductivity of  ${\rm TiO_2}$ .  $^{84}$ 

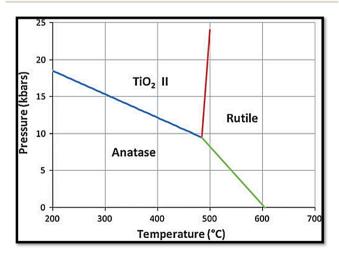


Fig. 3 Reaction boundaries of phase transitions in TiO<sub>2</sub>.<sup>74</sup>

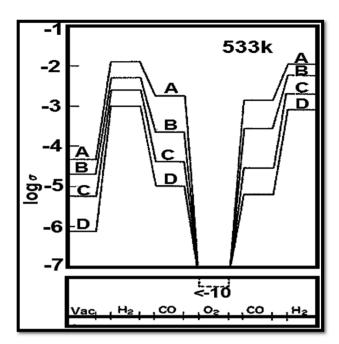


Fig. 4 Influence of gas cycle of sequence on electrical conductivity of 0.5%  $Pt/TiO_2$  doped with (A)  $W^{6+}$  (B)  $Ta^{5+}$  (C) undoped and (D)  $Mg^{2+,85}$ 

Vacancies for oxygen are the main fault in TiO<sub>2</sub>.<sup>70</sup> The absence of oxygen introduces electrons excess in the solid ensuing in a rise of conductance of electricity.70 Fig. 485 shows the influence of gas cycle of sequence on electrical conductivity of 0.5% Pt/TiO<sub>2</sub> doped with (A) W<sup>6+</sup> (B) Ta<sup>5+</sup>(C) undoped and (D) Mg<sup>2+</sup>. Another thing to be added is that Nb (niobium) or tantalum atoms act as electron donors86 when incorporated into TiO2. Besides, Nb (niobium) or tantalum atoms increase the electrical conductivity. On the other hand, chromium, manganese, and iron act as electron acceptors,87 decreasing or increasing the TiO2 electrical conductivity. On the ratio between the oxygen vacancy concentration and their concentration, the augment or reduction in electrical conductivity depends.88 To the electrical conductivity, the point defects typed imperfection plays a crucial role. It is reported that the ionization energies for titanium interstitials89 is 0.007-0.08 eV. To the electronic conduction, the contribution of oxygen vacancies is also important.90 Several reports recommended the presence of both phenomena, with an activation energy of carrier generation around 4 meV.91

After studying the formation energies and the electronic states of 4 types of lattice point defects in rutile, it was found that in the forbidden band, the existence of vacancy for oxygen leads to a deep donor defect level. Moreover, to establish that the band gap is  $\sim$ 2.86 eV, the band building of the pure rutile  ${\rm TiO_2}$  was studied.<sup>92</sup> The valence band (VB) of wide gap rutile and anatase are formed by  ${\rm O_{2p}}$  states, while titanium 3d states forms the conduction band (CB).<sup>70</sup> On these states, the detailed calculations can be found.<sup>45</sup> Recently, several researches have been reported that the electronic structure of rutile bulk can also be described by means of additional techniques used in the experiment such as electrical resistivity, electroabsorption, <sup>93,94</sup>

photoconductivity and photoluminescence, 95,96 X-ray absorption spectroscopy (XAS), 97-102 resonant Raman spectra 96,103 and photoelectrochemical analysis. 58,104

# Synthesis of TiO<sub>2</sub> nanostructures

There are some methods of making TiO<sub>2</sub> nanostructures. Gas phase and solution routes methods are the main ones. The solution route is able to coat complex shapes, to govern on stoichiometry, and preparation of composite materials. The presence of carbon as an impurity is an expensive precursor, and long processing times are the difficulties of solution route. There are two methods of synthesis (i) physical and (ii) chemical methods. Both methods have disadvantages and advantages. Physical procedures produce large quantities of material, but their resolution is inadequate to nanometers. The chemical procedures can approach the atomic layer limit<sup>105</sup> through the preparation of minor (e.g., <100 nm and often <10 nm) structures. Hence, at a smaller scale, chemical procedures are typically completed.

### 3.1 Solution procedures

3.1.1 Sol gel route. In materials science and ceramic engineering, a wet-chemical technique widely used is sol–gel process. The advantage of sol–gel process is inexpensiveness. With sol–gel method, nanostructured TiO<sub>2</sub> has been synthesized from titanium precursor hydrolysis. Usually, this method involve an acid catalyzed hydrolysis of titanium(IV) alkoxide tracked by condensation. This process includes 4 steps *i.e.* hydrolysis, polycondensation, drying and thermal decomposition. The sol–gel procedure includes the metal alkoxides usage, which suffer hydrolysis and condensation polymerization reactions to give gels as shown in these equations. 120

Hydrolysis:

$$Ti(OR)_4 + 4H_2O \rightarrow Ti(OH)_4 + 4ROH$$
 (1)

Condensation:

$$Ti(OH)_4 \rightarrow TiO_2 + 2H_2O$$
 (2)

where, R = ethyl, iso-propyl, *etc.* For the change of liquid sol into a solid gel phase, the whole polymerization leads to loss of solvent. The sol particles size depends on the composition of solution, temperature and pH.<sup>20</sup> Ti–O–Ti chains development is preferred with little amount of water, additional titanium alkoxide in the reaction combination and stumpy hydrolysis rates.

The advantages of sol-gel method are as follows:

- Product homogeneity.
- Good rheostat above powder particle shape and size and size distribution.
  - Easiness of manufacturing multi-component materials.
  - No particular apparatus with low price.
  - Low processing temperature.
  - Synthesis of films with high photocatalytic activity.

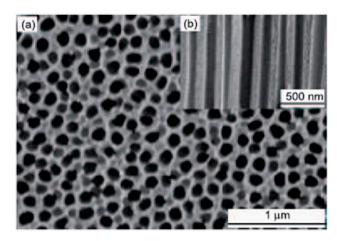


Fig. 5 SEM of AAM template, (a) top and (b) side views.

Utilizing sol–gel template method, the syntheses of  ${\rm TiO_2}$  nanotubes, nanorod and nanowires has been reported. This synthesis was carried out from the porous anodic alumina membranes (AAMs), supramolecular template and organogel. The first step for synthesis of nanorod is tumbling porous AAMs into a warmed  ${\rm TiO_2}$  sol following by drying and heating processes. Ghamsari and colleagues synthesized  ${\rm TiO_2}$  nanorod by sol–gel Template Process. Briefly, the porous anodic alumina of 60  $\mu$ m in thickness and pores of 100 nm in diameter were used as templates.

Fig. 5 and 6 show SEM images of AAM template and TiO<sub>2</sub> nanorods grown in the AAM template. By changing the dipping time, nanorods length can be changed. An individual TiO<sub>2</sub> nanorods picture is shown in Fig. 6(b). Through the full length of the rods and continuous yet the rode is uniform. To obtain the nanowire arrays of TiO<sub>2</sub>, electrophoretic deposition of TiO<sub>2</sub> colloidal suspensions can be used into the pores of an AAM.<sup>123</sup> At room temperature; in another procedure; titanium tetraisopropoxide (TTIP) is dissolved in ethanol followed by the

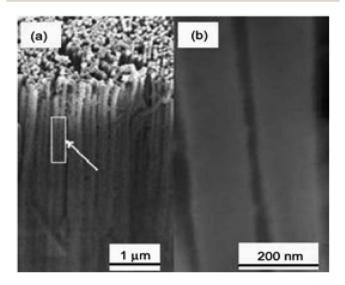


Fig. 6 SEM of  $TiO_2$  nanorods growth in AAM template, (a) low magnification image, (b) high magnification image.<sup>123</sup>

Review

(a)




Fig. 7 TEM images of TiO<sub>2</sub> nanoparticles after hydrothermal treatment of TBA peptized gel at (a) 210 °C and (b) 270 °C. 133

addition of glacial  $\mathrm{CH_3COOH}$  (mixed with demineralised water and  $\mathrm{EtOH}$ ) using  $\mathrm{HNO_3}$  as pH 2–3 controller. AAM is used as the cathode and platinum as an anode.  $\mathrm{TiO_2}$  nanowires are obtained after dissolving AAM template in 5% NaOH solution. Using titanium butoxide, titanium isopropoxide [TIPO] and titanium tetrachloride; as Ti precursors in HCl solution; have been synthesized. Nanotubes were also synthesized by Kasuga and colleagues 125–127 using sol–gel method with innermost and outside diameters of approximately 5 and 8 nm, respectively. The spine designed products were nanotubes.

**3.1.2 Hydrothermal procedures.** Hydrothermal syntheses are promising procedures to gain titania nanocrystalline particles. The hydrothermal process is effective to attain the crystalline phase at lower temperatures. Hydrothermal is broadly used for the manufacture of minor units in the ceramics industry. Generally, hydrothermal synthesis is known as crystal synthesis or crystal growth. Below 300 °C, the hydrothermal synthesis is usually carried out. 374 °C is the critical temperature and 22.1 MPa is the critical pressure of water under supercritical conditions.

Some studied indicated application of hydrothermal method to prepare TiO2 nanoparticles. 128-132 To synthesize TiO2 nanoparticles, hydrothermal treatment of titanium precursor (peptized precipitates) was also used.129 Besides, reaction of hydrothermal of titanium alkoxide under acidic ethanol-water solution was also used to prepare TiO2 nanoparticles. Under EtOH-H<sub>2</sub>O environment, TiO<sub>2</sub> nanoparticles synthesized were mainly primary structures of anatase. The sizes of the units were in range of 7-25 nm. Besides, TiO2 nanoparticles133 were synthesized using hydrothermal method. With increasing stirring for 45 minutes into distilled water at 1:4 volume ratio, 0.5 M solution of titanium butoxide Ti(OBu)<sub>4</sub> in 2-propanol was gradually added. To prepare nanoparticles for further examination, the gels prepared were treated hydrothermally. TEM images of TiO2 nanoparticles prepared using hydrothermal method are shown in Fig. 7.

Vijayalakshmi and Rajendran $^{134}$  synthesized  $TiO_2$  nanoparticles using hydrothermal method by making a water

solution of titanium. This solution was made by mingling one molar stoichiometric ratio of TTIP in 50 mL deionized water. TiO<sub>2</sub> nanowire in the solutions of 10 to 15 M sodium hydroxide were synthesized; using TiO2 white powders; without stirring within an autoclave at 150-200 °C for 24-72 h by Zhang and colleagues.135 Fig. 8 shows SEM and TEM images of nanowires of TiO2 prepared by Zhang and colleagues. 135 Titania nanotubes136 were synthesized via hydrothermal process. TiO2 powders were heated at 20-110 °C for 20 h. TiO2 nanotubes achieved were washed using a dil. HCl aqueous solution and deionized water. With NaOH aqueous solution, raw TiO2 material was treated. Besides, titania nanotubes137 were synthesized via hydrothermal. 5.0 g anatase TiO2 nanopowders were mixed with 180 mL 10 M NaOH in a perfluoroalkoxy (PFA) bottle and stirred for 1 h. The resultant precipitate was separated by centrifugation after hydrothermal reaction. Until pH value reached approximately 7, precipitate was rinsed with

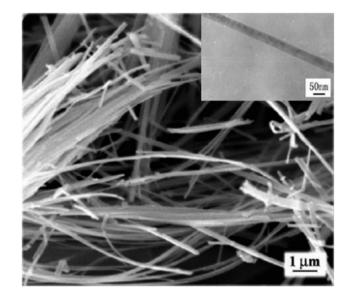



Fig. 8 SEM images of  $TiO_2$  nanowires and a TEM image of a single nanowire prepared by Zhang and colleagues.<sup>135</sup>

RSC Advances Review







Fig. 9 Electron microscopy images of (a) titania powders and (b) titania nanotubes.312






Fig. 10 TEM images of titania nanotubes at (a) low magnification and (b) high magnification.<sup>338</sup>

diluted HCl and demineralised water several times. Fig. 9 shows electron microscopy pictures of titania nanotubes and titania powders. Fig. 10 indicates the TEM pictures of TNTs; revealing that the TNTs have tubular, hollow and open structures. 3–6 nm is the inner diameter size of the TNTs and 1.9 nm is the average wall thickness. Besides, some other studies for syntheses of  ${\rm TiO_2}$  nanowires by hydrothermal are also available.  $^{\rm 110-115}$ 

3.1.3 Electrochemical procedures. To produce advanced thin films such as superlattice, epitaxial, nanoporous and quantum dot ones by anodization, electrochemical procedures provided a diversity and low temperature approach. The distinctive states of the films are measured by electrolysis parameters such as temperature, current density, potential and pH. <sup>138</sup> In a typical process, the conducting piece (undergoing anodization) is positioned in an electrolytic bath serving as anode. The cathode was a rod of platinum. From electrolyte to positive anode, at power supply the electrons are forced. Drifting through the power source, the electrons return to cathode. With hydrogen ions, these electrons react due to which bubbles off hydrogen gas are occurred. If oxide film is porous, the primary determinant is the electrolyte composition. Fig. 11<sup>139</sup> shows a representation of an electrochemical anodization cell.

In 2001, TiO<sub>2</sub> nanotube arrays fabrication through anodic Ti oxidation was reported first time.<sup>140</sup> Advanced studies

engrossed on extension of morphology,<sup>141</sup> length, pore size<sup>142</sup> and wall thickness<sup>143</sup> of the nanotube were carried out. Fig. 12<sup>144</sup> shows SEM of TA6V anodised in CA electrolyte under 5 V for 20 min. The usage of different electrolytic diluents permitted the architecture control from well detached, standalone nanotubes to tightly packed arrays. The wall thickness of typical nanotubes ranged from 5 to 30 nm, with 20 to 350 nm pore size and 0.2 to 1000 mm length. Zwilling and co-workers<sup>144</sup> used fluorinated electrolyte to produce a porous surface of TiO<sub>2</sub> films

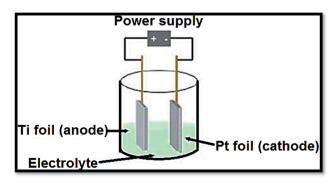


Fig. 11 Depiction of an electrochemical cell in which the Ti samples are anodized. Fabrication variables include temperature, voltage, pH and electrolyte composition.

pen Access Article. Published on 24 August 2018. Downloaded on 10/16/2025 4:59:42 AM.

Review RSC Advances

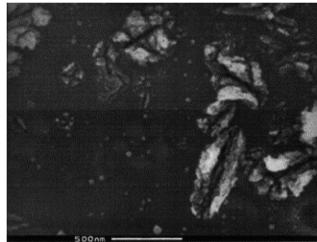


Fig. 12 Scanning electron micrograph of TA6V anodised in CA electrolyte. $^{144}$ 

via electrochemically anodization of titanium. Shimizu  $et\ al.^{145}$  reported that dil.  $\rm H_2SO_4$  could be used to bond porous  $\rm TiO_2$  thin films. Yamamoto  $et\ al.^{146}$  observed that the act of dye-sensitized solar cell device was better by cathodically electro-synthesized  $\rm TiO_2$  films; having sealed commercial Degussa P25 nanoparticles. Anodization or anodic oxidation of titanium foils was conducted by Patermarakis  $et\ al.^{147}$  Platinum and titanium were used as cathode and anode. Using formamide–water mixtures (having fluoride ions), Shankar and co-workers  $^{148}$  studied the effect of five dissimilar cationic species on development of  $\rm TiO_2$  nanotube array.

In 2006, Ruan and co-workers149 synthesized titania nanotube by titanium anodization in an electrolyte. In 2006, nanotube arrays of protracted length from DMSO electrolytes was described by Paulose and co-workers. 150 The importance of diethylene glycol (DEG) for nanotube array synthesis was reported by Yoriya and co-workers. 151 These authors investigated tube formation. The necessity of tube separation and crystallization in the DEG-based electrolytes were required. The benefit of TiO2 nanotubes produced by anodization is readily attachment capability in a perpendicular orientation onto the substrate; improving electron transfer pathways as compared to the non-oriented structure. 152 In one study, glycerol pH and water (75-25, v/v) electrolyte having 0.5% NH<sub>4</sub>F were modified using H<sub>2</sub>SO<sub>4</sub>.<sup>153</sup> The length of nanotube was 950 nm on adjusting pH 5.6 by H<sub>2</sub>SO<sub>4</sub>. Nanotubes of 16 mm were found by anodizing at 20 V for 8 h after adding of 0.1 M CH<sub>3</sub>COONa by maintaining pH at 5.6. TiO2 nanostructured as photoanodes were prepared by nanotubes of TiO2 by anodic oxidation of foil of titanium<sup>140,154-156</sup>. In a model experimentation, a plate of clean titanium was anodized in a 0.5% hydrogen flouride solution under 10-20 V for 10-30 min. The counter electrode used in the experiment was platinum. Crystallized TiO2 nanotubes were obtained by annellation of plate of anodized Ti at 500  $^{\circ}$ C for 6 hours in oxygen. The diameter and length of TiO<sub>2</sub> nanotubes may be optimized with the utilized potential between 1.0 and 25.0 V in optimized phosphate/HF

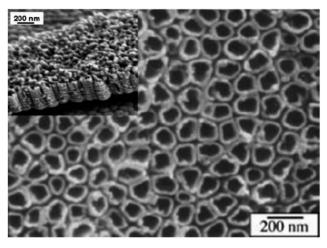


Fig. 13 SEM images of TiO<sub>2</sub> nanotubes prepared with anodic oxidation.<sup>159</sup>

electrolytes.<sup>158</sup> SEM pictures of TiO<sub>2</sub> nanotubes produced with this approach are shown in Fig. 13.<sup>159</sup> For the first time, H generation efficiency, phase evolution and electrochemical synthesis of anatase, anatase–rutile and anatase–rutile–brookite (ARB) TiO<sub>2</sub> nanotubes was reported Preethi *et al.*<sup>160</sup> The samples tubular morphology was confirmed by TEM and SEM.

### 3.2 Gas phase procedures

3.2.1 Chemical vapor deposition. The vapor deposition processes to form coatings to alter the mechanical, electrical are normally used. Also, these methods can be castoff to produce free-stand bodies, fibers and films, or to form fused materials. Recently, chemical vapor depositions have received great attention in the manufacture of nanomaterials. These processes occur in a vacuum space and if chemical reaction doesn't occur, these processes are called physical vapor deposition (PVD). In this process, gases must be heated by suitable thermal. By using liquid precursor and titanium tetraisopropoxide (TTIP), pyrolysis in a mixed gases (consisting of helium/oxygen atmosphere) leads to prepare bushy crystalline of TiO2 films with sizes below 10 nm.161 Ayllon et al.162 described the synthesis of amorphous nanoparticles of TiO2. Pradhan, et al.163 prepared nanorod arrays of TiO<sub>2</sub> with a length of 0.5-2 μm and a diameter of about 50-100 nm (Fig. 14). Metal organic CVD was used by the authors on a WC-Co substrate using (TTIP) as the precursor. Similarly, on the particle size distribution of aerosol particles prepared by gas-phase chemical reactions, Okuyama and colleagues164-166 described the effects of the primary concentration of TTIP vapor and temperature profile of the furnace. They found that in the controlled cylindrical furnace, the thermal decomposition of TTIP vapor led to form 10-60 nm sized ultrafine TiO2 nanoparticles. Likewise; using TTIP as precursor; the formation of TiO<sub>2</sub> nanoparticles reinforced on porous silica gel (60-100 mesh) via metalorganic chemical vapor deposition MOCVD process was reported by Ding and colleagues.167 A tubular furnace controlled the reactor temperature. Pretreatment of the support materials, CVD reaction and calcinations process were

RSC Advances Review

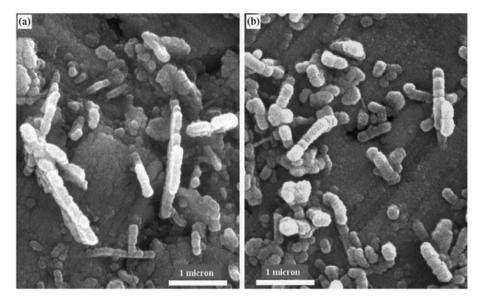


Fig. 14 SEM micrograph of TiO<sub>2</sub> nanowires deposited without NH<sub>3</sub> at 500 °C; (a) with 800 sccm argon flow, and (b) with 500 sccm argon flow. 163

involved in the synthesis of  ${\rm TiO_2}$  nanoparticle/silica gel photocatalyst. Contrarily, the fabrication of  ${\rm TiO_2}$  nanorods grown on fused silica substrates was reported by Wu  $et~al.^{168}$  Directly, the nanostructures of  ${\rm TiO_2}$  were grown on the substrates. The only one crystalline anatase and rutile  ${\rm TiO_2}$  nanorods were formed, respectively, when the temperature ranged between 630 and 560 °C at a pressure of 5 torr. Furthermore, for preparing of  ${\rm TiO_2}$  nanomaterial, the foregoing chemical vapor deposition approaches were also used. These included electrostatic spray hydrolysis, <sup>169</sup> diffusion flame pyrolysis, <sup>170</sup> ultrasonic spray pyrolysis, thermal plasma pyrolysis  $^{171-173}$  laser-induced pyrolysis  $^{174,175}$  and ultra-sonicated hydrolysis etc.

**3.2.2 Physical vapor deposition.** Among several techniques for the syntheses of TiO<sub>2</sub> nanowires, primary PVD procedures include ion implantation. Before growth of TiO<sub>2</sub> nanowires, a layer of Ti nanopowders deposited on the substrate was

Fig. 15 SEM images of the  $TiO_2$  nanowire arrays prepared by the PVD method.  $^{176}$ 

also reported by this group. $^{176,177}$  These authors used gold as catalyst. $^{176}$  Fig. 15 displays a model SEM image of nanowires of TiO $_2$  made by physical vapor deposition method. $^{176}$  Xiang et al. $^{179}$  reported deposit of TiO $_2$  nanowire on a Si substrate via thermal evaporation of Ti powder in a precise furnace. These authors molded SiO $_2$ /TiO $_2$  shell–core nanostructures by monitoring the preparation surroundings such as the time of reaction and the substrate position. $^{179}$  On a Si substrate, a two-steps thermal evaporation technique was used to grow TiO $_2$  nanowires. By a radio frequency coil, Ti powder was heated inside a quartz reactor under mixed gases composed of Ar-diluted O $_2$  atmosphere. $^{177-180}$ 

# 4. Applications of TiO<sub>2</sub> nanostructures

TiO2 nanostructures have several advantages making them as the most important existing resources with promising usage in the deferent areas. These unique features of TiO2 include electronic and short diffusion path. Generally, TiO2 nanomaterials are wide band gap semiconductors containing  $E_g$ -values ranging from 3.0 to 3.2 eV with high absorption in the UV region. Titanium dioxide (nanomaterial) is used an important material in high-tech applications. It is the most bio-compatible material. Its optical and biologically properties are responsible for UV protection applications. 181-184 As implant materials, TiO2 nanostructures are successfully used for dental, orthopedic and osteosynthesis applications.185 TiO2 suitable for optical applications.70 Besides, photochromism has also been observed in single crystal iron doped rutile.186 Today, the largest practical research on TiO<sub>2</sub> is its use for photo assisted organic molecules degradation.187 The applications utilizing this process are purification of waste water, disinfection and self-cleaning coatings in urban areas buildings. The following sub-sections describe different applications of nano TiO2 structures.

### 4.1 Photocatalytic applications

Review

Various semiconductor materials such as WO<sub>3</sub>, ZrO<sub>2</sub>, BiVO<sub>4</sub>, Fe<sub>2</sub>O<sub>3</sub> and NaTaO<sub>3</sub> have been developed and showed photocatalytic activities over the past few periods. Among of these, TiO<sub>2</sub> is the most photo-catalytically active material used for water splitting as well as decomposition of organic materials. 65,188-190 Hydrogen is environmental friendly and clean and, hence, it is considered as the future fuel. Numerous studies have been developed to produce hydrogen by splitting water. First of all in 1972, Fujishima and Honda4 reported the photocatalytic splitting of water in the occurrence of a TiO<sub>2</sub> catalyst. These materials have also been used to kill bacteria in water treatment<sup>191</sup> and tumor cells in cancer treatment.<sup>14,192</sup> Some reviews are available on the photocatalytic mechanisms. 11,16,24,33 By the absorption of photon  $hv_1$ , the photocatalytic mechanism is initiated manufacturing an electron-hole pair on the surface of TiO2 nanoparticle. An electron is encouraged to the conduction band (CB) with formation of a positive hole with the valence band (VB). One or more radicals or intermediate species involved in this photodecomposition process play a crucial role in the photocatalytic mechanisms of reaction. The different factors play significant roles in controlled photocatalytic activities of semiconductors. With constant adsorbents density on the surface, the semiconductors having large surface area lead to faster reactions on the surface. 193

The size of titanium dioxide particles is much correlated to the fraction of surface located atoms. Due to the decrease in particles dimensions, the atomic fraction enhancing the catalytic activities on the surface increases. The band gap energy depends on the size of nanoparticle. It increases with decreasing nanoparticle sizes, which can be exploited in the optimization of redox potential. The electrons in transmission band and the holes in valence band allow photoredox reactions easily. For high photocatalytic activity, the band gap permits only UV light to be proficiently used. Kormann and colleagues investigated the decomposition of 2-propanol using different sizes of  $\text{TiO}_2$  nanoparticles. The authors observed that photocatalytic activities of 7.0 nm particles were 1.6 times better than 15–30 nm size.

Wang et al.194 studied the decomposition of chloroform by TiO2 nanoparticles. They prepared TiO2 nanoparticles with different size particles and observed the best size of TiO<sub>2</sub> nanoparticles for chloroform photocatalytic decomposition. By decreasing particle size from 21 to 11 nm, an enhancement in activity was observed. Contrarily, by reducing to 6 nm, the activity decreased completely. The authors concluded that the optimal particle size was about 10 nm for this reaction. In different types of TiO2 nanomaterials, TiO2 nanorods, mesoporous TiO<sub>2</sub> and nanotubes have revealed high photocatalytic performances under the appropriate circumstances. 195-197 Rhodamine B was oxidized by mesoporous TiO2 by Peng et al. 196 On the oxidation reaction of desired materials, TiO2 mesoporous showed significant activity. The nanotubes of TiO2 treated with H<sub>2</sub>SO<sub>4</sub> solutions were prepared by Yang et al.<sup>197</sup> The authors observed that the TiO2 nanotubes treated with different concentration of H2SO4 solutions showed photocatalytic

activities for degradation of acid orange II. It was due to small particles having high specific surface areas of  $TiO_2$  nanotubes after treated with  $H_2SO_4$  solution.

To improve the photocatalytic activities under UV irradiation, metal doping TiO<sub>2</sub> nanomaterials have been primarily studied. In current years, wide research work has attentive on visible light tempted photocatalysis by metal doped semiconductor for improved photocatalytic act on the various organic pollutants degradation. 196-202 As potential dopants, several metal ions including iron<sup>203–205</sup> nickel<sup>206,207</sup> vanadium<sup>208</sup> chromium<sup>209</sup> platinum<sup>210</sup> ruthenium and cobalt ions<sup>211</sup> have been investigated. There are contradictory consequences on the effects of doping on the visible-light photoactivities of titanium dioxide. Non-metals such as N, C and S (as an impurity) have also been studied for their visible light photocatalytic activities.212-221 These studies informed that the non-metallic insertion enhanced photocatalytic actions as related to those for pure TiO<sub>2</sub> nanomaterials; particularly in the visible light region.<sup>213</sup> To obtain a charge balance, there are several procedures if an anion is substituted with a high valence anion. In TiO<sub>2</sub> lattice, nitrogen ions substitute oxygen atoms. Titanium dioxide nanotubes photocatalysts have been successfully prepared by Tokudome et al.219 The author investigated breakdown of gaseous isopropanol into carbon dioxide and acetone by Ndoped TiO<sub>2</sub> nanotubes. They observed that N-doped TiO<sub>2</sub> showed high photocatalytic oxidation activity when illuminated with visible light. Other points related to investigated photocatalytic activities of TiO2 doped sulfur(s) have also been reported.222 The results exhibited that in region of visible light S doped TiO2 showed a high photocatalytic activity but lower in UV region. Recently, carbon has received significant interest as a nonmetallic dopant in TiO2 materials. In visible light region, the decompositions of methylene blue and isopropanal have been demonstrated by C-doped TiO2.216 Using C-doped TiO2 nanoparticles, Shen and colleagues<sup>223</sup> reported the degradation of trichloroacetic acid under visible light. They observed that Cdoped titanium dioxide exhibited a remarkable photocatalytic activity for the reaction involved in degradation. Flouride doped TiO<sub>2</sub> was prepared by Yu et al.<sup>224</sup> The obtained F-TiO<sub>2</sub> displayed higher photocatalytic activity than undoped TiO2 under proper preparation conditions.224 For acetaldehyde and trichloroethylene decomposition, other comprehensive studies provided the investigated of N/F-doped TiO2 nanomaterials. It was reported that TiO<sub>2</sub> nanomaterials (N/F-doped) had high visible light photocatalytic activities for decomposition reactions. 225,226 The different dopants moieties metal and nonmetal doping titanium dioxide and preparation procedures are given in Table 2. On the other hand, this table comprises splitting of water by photochemical cell reaction over numerous photo catalysts (Table 3).

# 4.2 Photovoltaic applications

Fig. 16 exhibits the principle of a dye sensitized solar cells (DSSC).<sup>41</sup> Dye sensitized solar cells have involved much consideration as reformative low priced substitutes to usual solid state devices.<sup>227</sup> A DSSC composed a nanoporous film

**RSC Advances** 

Table 2 The different dopants moieties metal and nonmetal-doping titanium dioxide and preparation methods

| Kind of dopants  | Doped elements | Preparation methods   | Potential applications                                      | Ref. |
|------------------|----------------|---|---|------|
| Metal dopants    | Ag             | Silver nitrate was mixed with reduction agent (sodium citrate tribasic dihydrate) and the reaction temperature was raised to 80 °C with continuous stirring. Then TIP and HNO <sub>3</sub> were added and the reaction was maintained at 50 °C for 24 h. The prepared sol was   | Degradation of nitrophenol<br>in aqueous phase              | 316  |
|                  | Fe             | dried at 105 °C for 24 h and calcined at 300 °C The reactive magnetron sputtering method: 99.99%  | Wastewater decoloring                                       | 317  |
|                  |                | titanium target and 99.9% iron pieces were placed in the reaction chamber and mixture of argon and oxygen was introduced into the   |   |      |
|                  | V              | chamber during discharging Sol–gel method: solution 1 (vanadyl acetylacetonate dissolved in <i>n</i> -butanol) was mixed with solution 2 (acetic acid in titanium butoxide) and hydrolyzed (24 h) by the water generated <i>via</i> the esterification of acetic and butanol. The suspension as dried at 150 °C, pulverized and calcined at 400 °C for 0, | Wastewater decoloring                                       | 318  |
|                  | Au             | 5 h Titanium(w) butoxide dissolved in absolute ethanol was added to solution containing tetrachloroauric acid (HAuCl <sub>4</sub> ·4H <sub>2</sub> O), acetic acid and ethanol. The resulting suspension was aged (2 days), dried under vacuum, grinding and calcinated at 650 °C   | Wastewater decoloring                                       | 319  |
|                  | Pt             | Photoreduction process:<br>$TiO_2$ was suspended in<br>a mixture of<br>hexachloroplatinic acid in<br>methanol. The suspension<br>was irradiated with a 125 W<br>mercury lamp (60 min). Pt–<br>$TiO_2$ was separated by<br>filtration, washed with<br>distilled water and dried at<br>100 °C for 24 h  | Wastewater decoloring                                       | 320  |
| Nonmetal dopants | N              | Titanium nitride (TiN) oxidation: Heating of TiN at $450-550$ °C for 2 h in air (heating and cooling temperature rate: $2$ °C min <sup>-1</sup> )   | Photooxidation of aromatic compounds ( <i>e.g.</i> toluene) | 321  |
|                  |                | Treating anatase $TiO_2$ powder ST01 in the $NH_3$  | Photooxidation of acetaldehyde in gas phase                 | 322  |

Table 2 (Contd.)

| Kind of dopants | Doped elements   | Preparation methods                                    | Potential applications     | Ref. |
|-----------------|------------------|--|----------------------------|------|
|                 |                  | (67%)/Ar atmosphere at                                 |                            |      |
|                 |                  | 600 °C for 3 h   |                            |      |
|                 | S                | Oxidation annealing of                                 | Wastewater decoloring      | 323  |
|                 |                  | titanium disulfide (TiS <sub>2</sub> ) at              |                            |      |
|                 |                  | 300–600 °C   |                            |      |
|                 | N,S              | Hydrolysis of $Ti(SO_4)_2$ in                          | Photooxidation of volatile | 324  |
|                 |                  | $NH_3$ aqueous solution.                               | compounds in gas phase     |      |
|                 |                  | Precipitate was centrifuged,                           | (e.g. acetone and          |      |
|                 |                  | washed with distilled water                            | formaldehyde)              |      |
|                 |                  | and alcohol. Obtained gels                             |                            |      |
|                 |                  | were dried under vacuum at                             |                            |      |
|                 |                  | 80 for 10 h and were ground                            |                            |      |
|                 |                  | to obtain xerogel. The                                 |                            |      |
|                 |                  | xerogel was calcinated at                              |                            |      |
|                 |                  | 400–800 °C in air for 3 h                              | 71                         |      |
|                 | С                | Sol-gel method: TBOT was                               | Photooxidation of phenol   | 325  |
|                 |                  | hydrolyzed in the presence                             | compounds in aqueous       |      |
|                 |                  | of ethanol, water and nitric                           | phase                      |      |
|                 |                  | acid; precipitated titanium                            |                            |      |
|                 |                  | hydroxide was dried at<br>110 °C and calcinated in air |                            |      |
|                 |                  | at 150–200 °C  |                            |      |
|                 |                  | Acid-catalyzed sol–gel                                 | Photooxidation of phenol   | 326  |
|                 |                  | process. Alkoxidide                                    | compounds in aqueous       | 320  |
|                 |                  | precursor was dissolved in                             | phase                      |      |
|                 |                  | corresponding alcohol,                                 | phase                      |      |
|                 |                  | mixed with hydrochloric                                |                            |      |
|                 |                  | acid aqueous solution.                                 |                            |      |
|                 |                  | Obtained gel was aged for                              |                            |      |
|                 |                  | several days and calcinated                            |                            |      |
|                 |                  | in air (3 h at 65 °C and 3 h at                        |                            |      |
|                 |                  | 250 °C) and grounded                                   |                            |      |
|                 | В                | Anatase TiO <sub>2</sub> powder (ST01)                 | Improved photocatalytical  | 327  |
|                 |                  | was grinding with boric acid                           | activity                   |      |
|                 |                  | triethyl ester and calcinated                          | •                          |      |
|                 | in air at 450 °C |  |                            |      |
|                 | P                | Sol-gel method: TIP was                                | Photooxidation of phenol   | 328  |
|                 |                  | hydrolyzed in the presence                             | compounds in aqueous       |      |
|                 |                  | of isopropanol and water,                              | phase                      |      |
|                 |                  | after hydrolysis phosphoric                            |                            |      |
|                 |                  | acid was added. Dispersion                             |                            |      |
|                 |                  | was stirred for 2 h,                                   |                            |      |
|                 |                  | centrifuged at 3500 rpm and                            |                            |      |
|                 |                  | dried at 100 °C. Obtained                              |                            |      |
|                 |                  | powder was calcinated at                               |                            |      |
|                 |                  | 300 °C   |                            |      |

prepared from mesoporous oxide layer of anatase  $TiO_2$ . Firstly, through a transparent conducting oxide (TCO) electrode, cell is illuminated where  $TiO_2$  is deposited. Into the metal oxide conduction band, photo excited dye molecules insert electrons.  $I^-/IO_3^-$  couple acts as redox species in the electrolyte reducing the oxidized dye molecules back to their inventive state. Overall, the device produces electric power from light. The surface of nanoporous  $TiO_2$  film is bounded by more cations than the electrons. Henceforth, electron transport mechanism is measured to be purely diffusive. Prom solid-state p-n junction, the process of absorption of light and the transport in

the case of DSSCs are different due to distinct phenomenon. Through eqn (3) to (6), the process is described:

Sensitizer (S) + 
$$hv \rightarrow S^*(excited)$$
 (3)

$$S^* + TiO_2 \rightarrow e^-(TiO_2) + oxidized sensitizer^+$$
 (4)

Oxidized sensitizer<sup>+</sup> + 
$$3/2 I^- \rightarrow S + 1/2 I_3^-$$
 (5)

$$1/2 I_3^- + e^-$$
(counter electrode)  $\rightarrow 3/2 I^-$  (6)

Table 3 Water splitting by photochemical-cell reaction over various photocatalysts

| Photocatalysts  |         | Reaction solutions                     |  | Rate of evolutions $(\mu \text{mol } h^{-1})$ |       |      |
|---|---------|--|--|---|-------|------|
|   | Weights |  | Light sources  | $O_2$   | $H_2$ | Ref. |
| Pt/TiO <sub>2</sub>   | 0.3 g   | 2.17 M Na <sub>2</sub> CO <sub>3</sub> | 400 W Hg lamp  | 568   | 287   | 329  |
| $ZrO_2$   | 1 g     | Distilled water                        | 400 W Hg lamp  | 72  | 36    | 330  |
| $ZrO_2$   | 1 g     | 1.09 M Na <sub>2</sub> CO <sub>3</sub> | 400 W Hg lamp  | 142   | 75    | 330  |
| Pt/ZrO <sub>2</sub>   | 1 g     | 0.94 M NaHCO <sub>3</sub>              | 400 W Hg lamp  | 120   | 61    | 330  |
| $Ru_2O/ZrO_2$   | 1 g     | Distilled water                        | 400 W Hg lamp  | 11  | 5     | 330  |
| Cu/ZrO <sub>2</sub>   | 1 g     | Distilled water                        | 400 W Hg lamp  | 14  | 6     | 330  |
| NiO/Sr <sub>2</sub> Nb <sub>2</sub> O <sub>7</sub>          | 1 g     | Distilled water                        | 400 W Hg lamp  | 110   | 36    | 331  |
| NiO/Sr <sub>2</sub> Ta <sub>2</sub> O <sub>7</sub>          | 1 g     | Distilled water                        | 400 W Hg lamp  | 1000  | 480   | 331  |
| (Tetra)BaTa <sub>2</sub> O <sub>6</sub>                     | 1 g     | Distilled water                        | 400 W Hg lamp  | 21  | 10    | 332  |
| (Ortho)BaTa <sub>2</sub> O <sub>6</sub>                     | 1 g     | Distilled water                        | 400 W Hg lamp  | 33  | 15    | 332  |
| (Ortho)BaTa <sub>2</sub> O <sub>6</sub>                     | 1 g     | 0.0005 M Ba(OH) <sub>2</sub>           | 400 W Hg lamp  | 126   | 59    | 332  |
| (Ortho)BaTa <sub>2</sub> O <sub>6</sub>                     | 1 g     | 0.001 M KOH                            | 400 W Hg lamp  | 24  | 11    | 332  |
| (Ortho)BaTa <sub>2</sub> O <sub>6</sub>                     | 1 g     | $0.0005~\mathrm{M~BaCl_2}$             | 400 W Hg lamp  | 15  | 6     | 332  |
| NiO/BaTa <sub>2</sub> O <sub>6</sub>                        | 1 g     | Distilled water                        | 400 W Hg lamp  | 629   | 303   | 332  |
| Ni/Rb <sub>4</sub> Nb <sub>6</sub> O <sub>17</sub>          | 1 g     | Distilled water                        | 400 W Hg lamp  | 936   | 451   | 333  |
| Ni/K <sub>4</sub> Nb <sub>6</sub> O <sub>17</sub>           | 1 g     | Distilled water                        | 400 W Hg lamp  | 403   | 197   | 333  |
| Pt/TiO <sub>2</sub> , TiO <sub>2</sub>                      | 12 mg   | $2$ M KBr, $6.5$ mM FeCl $_2$          | 500 W Hg   | 2.8   | 1.3   | 334  |
| Pt-TaON, Pt-WO <sub>3</sub>                                 | 0.2 g   | 5 mM NaI                               | 300 W Xe lamp with filters: $\lambda > 420 \text{ nm}$ | 24  | 12    | 335  |
| Pt/BaTaO <sub>2</sub> N, Pt/WO <sub>3</sub>                 | 0.1 g   | 5 mM NaI                               | 300 W Xe lamp with filters: $\lambda > 420 \text{ nm}$ | 6.6   | 3.1   | 336  |
| Pt/SrTiO <sub>3</sub> :Rh, BiVO <sub>4</sub>                | 0.1 g   | 2 mM FeCl <sub>3</sub>                 | 300 W Xe with filter: $\lambda > 420 \text{ nm}$       | 15  | 7.2   | 337  |
| Pt/SrTiO <sub>3</sub> :Rh, Bi <sub>2</sub> MoO <sub>6</sub> | 0.1 g   | 2 mM FeCl <sub>3</sub>                 | 300 W Xe with filter: $\lambda > 420 \text{ nm}$       | 19  | 8.9   | 235  |

From the equations, it is clear that photosensitizer (S) adsorbs light on the exterior of the semiconductor  $TiO_2$  (eqn (3)). Then the photo-excited dye (S\*) hand over electrons into titanium dioxide (eqn (4)). After that the reduced species found in the electrolyte (I<sup>-</sup>) recovers electrons losing in the sensitizer (eqn (5)). Finally, by the mediator (I<sub>3</sub><sup>-</sup>) that gains electrons (eqn (6)), the circuit is closed.

# 4.3 Photocatalytic water splitting

Photo-electrochemical and photo-catalytic water splitting to produce hydrogen are considered as potential procedures to achieve hydrogen. These are discussed below.

4.3.1 Fundamentals of photocatalytic water splitting. At semiconductor electrodes, breakdown of water is the main aim of lively research in current years. First, on a TiO2 electrode, photocatalytic splitting of water was reported by Fujishima and Honda<sup>4</sup> in 1972. For green and sustainable energy sources, <sup>230</sup> photocatalytic water splitting into H2 and O2 using TiO2 nanomaterials remains to be challenge. To drive chemical reactions, the generated electron and hole can be used. Water molecules for overall water splitting231-233 are oxidized as well as reduced. The oxidation of water takes place by the holes to form  $O_2$ . While the reduction of water takes place by the electrons to form H<sub>2</sub>. Of course, there are several features of TiO<sub>2</sub> but under solar energy, its photocatalytic water splitting efficacy is still quite low. Consequently, to activate the photocatalyst, only UV light can be utilized. It enhances its visible light response including upgraded bulk properties of the material. Water splitting mechanism on TiO2 for hydrogen production is shown in Fig. 17.

4.3.2 Water splitting on TiO<sub>2</sub> nanotube arrays. TiO<sub>2</sub> nanotubes photocatalysts was investigated for water splitting under UV illumination by Shankar et al. 143 By potentiostatic anodization of titanium foil at 10 V in an electrolyte consist of (0.5% hydrofluoric acid, CH<sub>3</sub>COOH mixed in a 7:1 ratio), 143 the TiO<sub>2</sub> nanotubes were prepared. Besides, four different electrolyte bath temperatures i.e. 5 °C, 25 °C, 35 °C, and 50 °C were tried to obtain the variation in the nanotubes length and thickness. TiO<sub>2</sub> nanotubes having pore diameter of 22 nm and wall thickness of 34 nm (ref. 156) were used to generate hydrogen gas. The total adaptation efficiency was 6.8%. 156 At 320-400 nm (98 mW cm<sup>-2</sup>), the authors also reported that for illumination. The nanotube array of TiO<sub>2</sub> photoanodes may generate hydrogen from water with 12.25% photoconversion efficiency. On titanium foil; nanotube arrays with 570 nm in length and 70 nm in pore size; were prepared in 0.15 M hydrofluoric acid-0.5 M nitric acid by Xie et al.217 Fig. 18 shows the comparison between the photoelectrochemical current of annealed TiO<sub>2</sub> nanotube array films and that of porous TiO2. To higher surface area, the nanotube array samples with higher electrochemical current density were also ascribed.

**4.3.3 Water splitting on doped TiO**<sub>2</sub>. Splitting of water has also been studied on TiO<sub>2</sub> obtained after doping with metalnon metals. Exactly doping is the incorporation of foreign elements into TiO<sub>2</sub> crystal lattice. The aim of doping is to enhance photocatalytic activities.<sup>234</sup> With the potential for H<sub>2</sub> evolution, certainly the band gaps of titanium dioxide semiconductor photocatalysts become extensive.

In a photoelectrochemical cell to oxidation and reduction of water to H<sub>2</sub> and O<sub>2</sub>, Wrighton and colleagues<sup>235</sup> investigated the

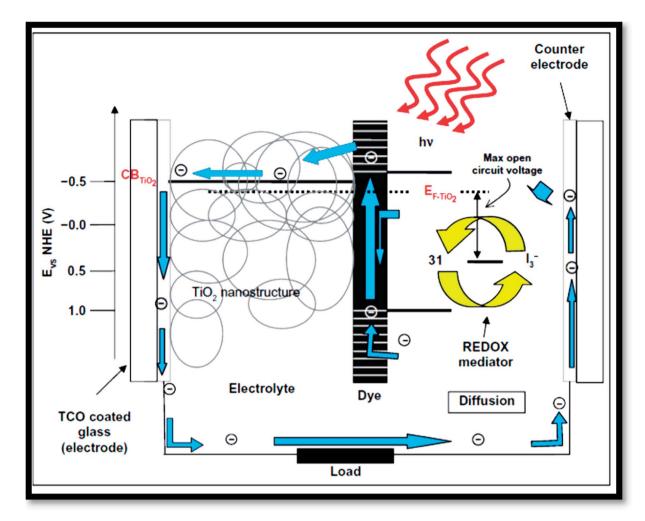


Fig. 16 Operation principles and energy levels of nanocrystalline dye-sensitized solar cell.<sup>41</sup>

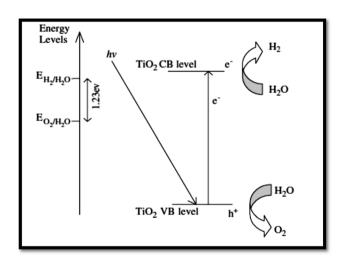


Fig. 17 Mechanism of  ${\rm TiO_2}$  photocatalytic water-splitting for hydrogen production.  $^{230}$ 

use of an n-type semiconductor  $SrTiO_3$  electrode. Without any external bias, decomposition of  $H_2O$  can be driven photochemically. Jin and co-workers<sup>236</sup> reported that  $TiO_2$  doped with

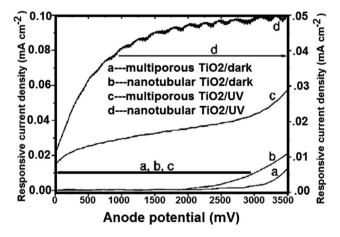


Fig. 18 Measured current of crystallized porous and nanotubular  $TiO_2/Ti$  electrodes under linearly swept potential from 0 to 3500 mV vs. SEC.<sup>217</sup>

platinum/boron was a good system for splitting of water. Besides, Khan and colleagues<sup>237</sup> described the response for splitting of water on TiO<sub>2</sub> doped with carbon. The total conversion efficiency was 11%, which had a high water splitting

**RSC Advances** Review

performance. The authors noted that at 40 mW cm<sup>-2</sup> illumination, an extreme photo-conversion efficiency of 8.35% could be obtained. The synthesis of TiO<sub>2</sub> nanocrystalline thin films; with Pt-loaded through use of radio frequency magnetron sputtering method (RF); was described by Matsuoka et al.<sup>238</sup> They investigated that visible light was responsive for water decomposed in the occurrence of TiO2 nanocrystalline.239 Bocharov et al.240 estimated theoretically the photocatalytic fitness of tinniest single wall fluorite structured titania (4,4) nanotube (NT) possessing three layers each (O-Ti-O) and doped by V, Ni, Mn, Sc, Cr, Fe, Co, Zn and Cu atoms substituted for host Ti atoms. They had associated electronic structure of ground state. For splitting of water, the results were in favor of Sc-doped titania nanotubes only for a potential photocatalytic usage. Using the sol-gel technique, Guayaguil et al. 241 synthesized a series of mesoporous TiO<sub>2</sub> (meso-TiO<sub>2</sub>). At 500° and 550°, they were calcined following synthesis. For H generation, the mesoporous 2.50 wt% Pt-TiO2 had the maximum photoactivity that was displayed by the prepared semiconductors. Alitabar et al. 242 increased the photocatalytic activity of TiO<sub>2</sub> nanotube arrays used as a photoanode in water splitting by doping it with sodium and carbon.

4.3.4 Water splitting on dye sensitized TiO2. To increase the photocatalytic reaction efficiency, one of the ways is to couple TiO2 semiconductor nanomaterials to an organic dye to employ visible light for energy change. Some dyes with visible light sensitivities can be utilized in photocatalytic systems and solar cells. 243-245 Duonghong and co-workers 246 studied the effect of using Ru(bipy)<sub>3</sub><sup>2+</sup> as a dye sensitizer under visible light radiation for hydrogen gas production. They reported water decomposition by using [Ru(bipy)<sub>3</sub>]<sup>2+</sup> and rhodamine B under visible light. Besides, the effect of utilizing  $[Ru(dcpy)_2(dpq)]^{2+}$  as a dye sensitizer, Alitabar and Yoozbashizadeh242 carried out a parametric investigation on photocatalytic splitting of water for hydrogen gas manufacture under visible light irradiation. Hydrogen production was increased when dye molecules were adsorbed on to TiO2. With the help of structure directing surfactant, Sreethawong et al.247 prepared mesoporousassembled TiO2/Pt. Furthermore, the nitrogen doped TiO2/Pt (N-TiO<sub>2</sub>) was prepared *via* calcination of the hydrolysis product of Ti(SO<sub>4</sub>)<sub>2</sub> with aqueous ammonia followed by platinum loading by Li et al.248 N-TiO2/Pt was sensitized and used for hydrogen production in occurrence of triethanolamine using anhydrous EtOH solution of eosin Y. Under comparable experimental conditions, it was observed that eosin Y-N-TiO<sub>2</sub>/ Pt exhibited advanced photocatalytic activity than eosin Y-TiO<sub>2</sub>/ Pt.

4.3.5 Water splitting on modified TiO2. Many scientists have modified TiO2 by different compounds to augment the process of water splitting. Over the surface of TiO2, when silver oxide nano clusters were impregnated, Mandari et al.249 synthesized plasmonic Ag<sub>2</sub>O/TiO<sub>2</sub> photocatalysts. Zhang et al.<sup>250</sup> synthesized (g-C<sub>3</sub>N<sub>4</sub>) graphitic carbon nitride nanosheets/ titanium dioxide (TiO2) nanoparticles hetero-structure. The prepared g-C<sub>3</sub>N<sub>4</sub>/TiO<sub>2</sub> hetero-structured composites showed excellent photocatalytic hydrogen generation. Besides, on the g-C<sub>3</sub>N<sub>4</sub> nanosheets the TiO<sub>2</sub> nanoparticles were well dispersed.

The as obtained g-C<sub>3</sub>N<sub>4</sub> coupled with TiO<sub>2</sub> not only increased the surface area of g-C<sub>3</sub>N<sub>4</sub>, but also promoted the separation of photo-generated charge carriers. Hou et al.251 used two typed gold films (i) coated with TiO2 (ii) and uncoated with TiO2. After that, they reported measurements of photocatalytic water splitting. For hydrogen gas production with Pt and CoO<sub>r</sub> as dual cocatalysts, Zhang et al.252 reported a new CoOx/TiO2/Pt photocatalyst. This type of catalyst was prepared by template assisted atomic layer deposition (ALD). Under UV light irradiation, the generated electrons and holes transfer to the different surfaces of TiO2 nanotubes. Photocatalytic efficiency of CoOx/TiO2/Pt photocatalysts was 275.9 μmol h<sup>-1</sup>, while that pristine TiO<sub>2</sub> nanotubes was 56.5 μmol h<sup>-1</sup>. Xu et al.<sup>253</sup> synthesized novel plate like Co(OH)<sub>2</sub> decorated TiO<sub>2</sub> nanosheets for photocatalytic hydrogen generation illustrating Co(OH), decorated TiO, samples of high rate of hydrogen generation than native TiO2 sample. Sui et al.254 prepared a Pt/TiO2 catalyst, where Pt was atomically and selectively dispersed on the (1 0 1) facets of nanosized TiO<sub>2</sub> single crystals. For H<sub>2</sub> production, a remarkably higher photocatalytic activity was compared to frequently used Pt/TiO2. Si et al. 255 synthesized anatase TiO2, thin TiO2 (B) nanosheets and their composites. The properly aligned structure of band, with the conduction band level of ultra-thin TiO2 (B) was about 0.6 eV higher than that of the anatase. Wang et al. 256 reported that very small amount of fluorine inhibited hydrogen and oxygen recombination. The detailed study showed that inhibition was by occupation of hydrogen and oxygen sorption and activation sites by fluorine ion over platinum. Liu et al. 257 fabricated a composite photoanode having TiO2 nanotube arrays altered with polyoxometalate (POM) and Co<sub>9</sub>S<sub>8</sub>.

#### 5. Mechanism of water splitting

On surface modification of TiO2, a number of efforts have been made to expand the photocatalytic activities as simple change can eagerly adjust the mechanisms and accelerates the kinetics of photocatalysis. 258,259 In the UV regime, the band gap for TiO2 lies. Besides, the latter has lower photocatalytic activities due to the lower ECB of ritual by  $\sim 0.2$  eV. For modification of TiO<sub>2</sub> nanomaterials, the goals are to improve their optical activities. 213,214 There are several methods to recover the performance of TiO2 nanomaterials. In visible light, other colorful compounds sensitizing TiO2 might be improved optical activity. Second, doping with other elements can also change the optical properties of TiO<sub>2</sub> nanomaterials. At the atomic level, Hussain et al.260 explored the interfacial structure between a rutile TiO<sub>2</sub>(110) surface pre-characterized and liquid water. The mechanism of splitting of water occurring in the occurrence of semiconductor photocatalyst was explained by Salvador in 1-4 equations as follows.261

Semiconductor + 
$$2h\nu \rightarrow 2h^+ + 2e^-$$

$$H_2O + 2h^+ \rightarrow \frac{1}{2}O_2 + 2H^+(E_{O_2/H_2O})$$

Review RSC Advances

$$2H^{+} + 2e^{-} \rightarrow H_{2}(E_{H_{2}O/H_{2}})$$

$$H_2O \xrightarrow{h\nu} H_2(g) + \frac{1}{2}O_2(g)$$

EtOH serves as a sacrificial reagent which also helps to increase the entire process efficiency.<sup>64</sup> Water splitting mechanism on Ag/TiO<sub>2</sub> was explained by Liu *et al.*<sup>262</sup>

According to Salvador  $et~al.^{261}$  during the process of water splitting, formation of  $H^+$  and  $OH^-$  can take place through the reaction of  $H_2O$  molecules with holes in  $TiO_2$  valence band. The consumption of  $\cdot OH$  can occur through chemical reaction with  $CH_3CH_2OH$ . With enhanced energy, the electrons react with  $H^+$  at the surface of Ag NPs where  $H^+$  can take an electron through SPR (surface plasmon resonance) to generate an H atom, and then 2H atoms associate with each other for the formation of an  $H_2$  molecule.

$$TiO_{2} + h\nu \rightarrow h_{\nu b}^{+} + e_{cb}^{-}$$

$$e_{cb}^{-} \rightarrow e_{Ag}^{-}$$

$$e_{Ag}^{-} + h\nu(visible) \rightarrow e_{SPR}^{-}$$

$$h_{\nu b}^{+} + H_{2}O \rightarrow \cdot OH + H^{+}$$

$$CH_{3}CH_{2}OH + \cdot OH \rightarrow CH_{3}COOH + H^{+}$$

$$e_{SPR}^{-} + H^{+} \rightarrow H$$

$$H + H \rightarrow H_{2}$$

With an  $I^-/IO_3^-$  (iodide/iodate) redox-mediator system, water splitting mechanism on  $TiO_2$  was explained by Nishijima et al. 263 Besides, they studied the photoassisted oxidation of water continued with impartially high efficiency when  $Fe^{3+}$  ions were used as electron acceptors. This whole process of splitting of water on doped titanium dioxide; containing a rutile phase; was compared to that on doped titanium dioxide with an anatase phase. After all, they proposed the mechanism of water splitting in following equations:

$$TiO_{2} + h\nu \rightarrow e^{-} + h^{+}$$

$$2H_{2}O + 4h^{+} \rightarrow O_{2} + 4H^{+}$$

$$Fe^{3+} + e^{-} \rightarrow Fe^{2+}$$

$$C_{2}H_{5}OH + 3H_{2}O + 6h^{+} \rightarrow 2CO_{2} + 6H^{+}$$

$$2H^{+} + 2e^{-} \rightarrow H_{2}$$

$$4OH^{-} + 4h^{+} \rightarrow O_{2} + 2H_{2}O$$

$$IO_{3}^{-} + 3H_{2}O + 6e^{-} \rightarrow I^{-} + 6OH^{-}$$

$$2H_2O + 2e^- \rightarrow H_2 + 2OH^-$$
  
 $I^- + 6OH^- + 6h^+ \rightarrow IO_3^- + 3H_2O$ 

Mechanism for water splitting on  $TiO_2$  photosensitized by glutathione capped metal nanoclusters was explained by Chen and Kamat.<sup>264</sup> In aqueous buffer solution (pH = 7), a mesoscopic  $TiO_2$  film photosensitized by glutathione capped metal nanoclusters (Aux-GSH NCs) was utilized as the photoanode with platinum counter electrode. After all, they also proposed the water splitting mechanism as follows:

$$Au_{x} - GSH \xrightarrow{h\nu} Au_{x} - GSH^{*}$$

$$Au_{x} - GSH^{*} \cdots TiO_{2} \rightarrow Au_{x} - GSH^{+} \cdots TiO_{2}(e)$$

$$TiO_{2}(e) + Pt \rightarrow TiO_{2} + Pt(e)$$

$$Pt(e) + H^{+} \rightarrow 1/2H_{2}$$

$$Au_{x} - GSH^{+} + 1/2H_{2}O \rightarrow Au_{x} - GSH + 1/4O_{2} + H^{+}$$

$$Au_{x} - GSH^{+} \xrightarrow{accumulated holes} Au_{x} - GSH^{\nu+}$$

$$Au_{x} - GSH^{+} + EDTA \rightarrow Au_{x} - GSH + oxidized EDTA$$

## Lithium batteries

As the most promising energy storage technologies, lithium ion batteries (LIBs) are measured as the best for renewable energy, electric vehicles and mobile electronics. In recent years, as a possible anode,  $TiO_2$  (B) has received growing interest for Li ion batteries. As compared to commercialized  $Li_4Ti_5O_{12}$ , it offers higher energy storage. From the micron to the nanoscale, it is better than rutile and anatase. The important factors playing an important role and greatly affect the lithium ion batteries (LIB) performance are particle size and crystallographic alignment of the nanostructured. East-267 The crystallographic orientations [such as  $TiO_2$ (B)] and the theoretical studies confirmed that lithium ion mobility favors the direction in the order of b > c >> a-axis channel.

# 7. Gas sensors

The other application of  $TiO_2$  nanocrystalline is as gas sensor because gas adsorption causes a change in electrical conductivity like ZnO semiconductors. Thus,  $TiO_2$  is usually used as an oxygen gas instrument, *e.g.* to gauge the burning process of fuel in car engines to control fuel environmental pollution and consumption. Grimes *et al.* Stochastic considered the use of titanium dioxide as sensor.

8. White pigments

The pigment being the most abundant component in the coating affects the properties of the coating materials. Because of its highest refractive index of stability, colorless, and relatively low and uniform absorption of visible light, titanium dioxide has newly become a core white pigment source of scattering of light. By two procedures *i.e.* hydrothermal and hydrolysis, Samya El-Sherbiny *et al.*<sup>273</sup> created anatase and rutile. In paper coating, the usage of the prepared nanopigments disclosed that a slight amount of titanium dioxide was satisfactory to attain important improvements in brightness and opacity. It is due to ability of scattering light.

# 9. TiO<sub>2</sub>-based nanocomposites as catalysts

TiO<sub>2</sub> photo catalysts have been widely studied for the uptake of organic contaminants in water and air.274 The present article also concentrated on hybrid nanocrystals based on TiO2, describing different examples of synthetic methods and deliberating their applications in water treatment. Some papers are reported in the area of hybrid nanocrystals preparation. The papers on the photocatalytic features of nanocatalysts indicated their huge measure applications as challenges. However, these nanomaterials hold good assurance for the dilapidation of organic and inorganic contaminants in water or gas phase. The main features of nano sized TiO2 materials are enormously high surface to volume ratio and turning into a great density of catalytically surface sites.<sup>275</sup> The another fact is the size reliant band gap of nano sized semiconductors. It is likely to finely adjust the redox potentials of photogenerated electron hole couples to selectively control photochemical reactions. Besides, the catalyst surface is occupied easily by charges photogenerated in nano-catalysts.276 The hybrid nanocrystals formed by two or more components hold great promise for the development of multifunctional nanocatalysts among the embarrassment of methods proposed in the literature so far.277-281 Indeed, the opportunity is offered by hybrid nanocrystals to merge in one material resulting in countless possible combinations. 282-285 Under visible light irradiation, spatial separation of e<sup>-</sup>/h<sup>+</sup> could also be provide by the photoactivity hybrid nanocrystals. Thus, improving is an occasion to magnetically recuperate the photocatalysts or stimulate biocidal utility even in the dark. The surface properties, the particle size of the catalysts, their morphology, the composition, organization of the metal and TiO2 are the factors, which also affect the photocatalytic efficiency.<sup>286</sup> Therefore, for the preparation of metal nanoparticle hybrid hetero-structures, numerous synthetic methods have been described, which include impregnation,287 irradiation,288 electrodeposition,289 sonochemistry,290 hydrothermal,<sup>291</sup> sol-gel,<sup>292</sup> and flame-spray synthesis.<sup>293</sup> Wenging et al.294 prepared nanocomposites of titanium dioxide (P25) and reduced graphene oxide (RGO) utilizing numerous methods such as hydrazine reduction, UV-assisted photocatalytic reduction and hydrothermal. Those nanocomposites

were studied as photocatalysts for the progress of hydrogen from alcohol solution under UV-vis irradiation. It was found that the assimilation of RGO into P25 considerably increased the photocatalytic activity for H2 evolution, and the P25-RGO composite synthesized by the hydrothermal method showed the excellent presentation. Deepa et al. 295 prepared Au/TiO2 nanocomposites for photocatalytic hydrogen generation in the company of a sacrificial electron donor like ethanol or methanol under UV-visible and visible light irradiation. These nanocomposites exhibited excellent photocatalytic activity for hydrogen generation under UV-visible conditions. Amount of hydrogen evolved using Au/TiO2 nanocomposites under dark condition was zero. Anna and Jerzy296 studied the hydrogen generation by water splitting on Pt-TiO2 catalyst. Besides, they also examine the influence of numerous sacrificial chemicals like MeOH, Na<sub>2</sub>S, and ethylene diamine tetraacetic acid (EDTA), I and IO<sub>3</sub> ions on the photocatalytic efficacy in water splitting reactions in ultraviolet (UV) illumination. Photocatalytic water splitting was achieved at EDTA and Na2S utilization as the sacrificial reagents. Yatskiv et al.297 reported that the photocatalytic systems having mesoporous TiO2 and Pd/SiO2, produced extra quantities of molecular hydrogen at keeping in dark after the ending of irradiation. Václav and Daniela298 prepared TiO<sub>2</sub>/ZnS/CdS composites by homogeneous hydrolysis of aqueous solutions mixture of TiO2SO4, ZnSO4, and CdSO4 with thioacetamide for photocatalytic hydrogen production from water. Hydrogen generation was seen in the company of Pd and Pt nanoparticles deposited on TiO<sub>2</sub>/ZnS/CdS composites. The excellent photocatalytic activity for H2 evolution indicated with TiZnCd<sub>7</sub> on surface deposited with palladium, which had 78.5% ZnS, 20.21% TiO2, and 1.29% CdS·TiO2/ZnS/CdS. Quanjun et al.299 reported new composite material having of TiO<sub>2</sub> nanocrystals via two steps hydrothermal process utilizing thiourea, sodium molybdate and graphene oxide as precursors with tetrabutylorthotitanate and MoS<sub>2</sub>/graphene hybrid as titanium precursors. TiO2/MoS2/graphene composite attained high  $H_2$  generation rate of 165.3  $\mu$ mol h<sup>-1</sup> without a noble metal cocatalyst. Anna et al.300 interpreted the development of the quantum yield of H<sub>2</sub> generation using TiO<sub>2</sub>/Ag<sup>0</sup> to TiO<sub>2</sub>/Ni<sup>0</sup> to TiO<sub>2</sub>/Cu<sup>0</sup> in terms of alterations in the electronic interface between the semiconductor surface and metal nanoparticles. They observed a controlled metal amount range for maximum quantum yield of hydrogen generation. Ke et al.301 examined Ptloaded nanocomposites, pristine MWNTs and TiO2 for their photocatalytic activities for water splitting with triethanolamine as an electron donor. Hydrogen was effectively generated on Pt/ MWNT-TiO<sub>2</sub> in visible light illumination ( $\lambda > 420$  nm). Hydrogen production rate up to 8 mmol g<sup>-1</sup> h<sup>-1</sup> under full spectral irradiation of a Xe-lamp, or more was attained. Takuya et al.302 investigated the photocatalytic hydrogen generation in  $MeOH_n$  with  $CuO/TiO_2$ ,  $SnO/TiO_2$ ,  $ZnO/TiO_2$ ,  $CuO/Al_2O_3/TiO_2$ and Al<sub>2</sub>O<sub>3</sub>/TiO<sub>2</sub> nanocomposites. The maximum hydrogen generation was achieved with CuO/Al<sub>2</sub>O<sub>3</sub>/TiO<sub>2</sub> nanocomposites having 0.3 wt% Al<sub>2</sub>O<sub>3</sub>/TiO<sub>2</sub>/0.2 wt% CuO. Nitish et al.<sup>303</sup> demonstrated the higher hydrogen evolution reaction (HER) activity of Pt nanoparticles (Pt NPs) reinforced on titanium dioxide (TiO2) nanocrystals (Pt-TiO2) and nitrogen doped

Review **RSC Advances** 

reduced graphene oxide (N-rGO) constructed TiO2 nanocomposite (Pt-TiO<sub>2</sub>-N-rGO). Lu et al.304 prepared TiO<sub>2</sub> photocatalysts with nickel sulfide co-catalyst by stocking nickel sulfide on TiO2 with solvothermal synthesis method. It was reported that NiS was used as a co-catalyst with TiO2 for the photocatalytic generation of H<sub>2</sub>. High hydrogen generation was achieved with NiS as hexagonal structure with content in the composite of 7 at% in relation to TiO<sub>2</sub>. The rate of H<sub>2</sub> generation was augmented by 30 times than that of TiO2 alone. Fuyun et al.305 prepared nanocomposite of N-doped TiO2 with graphene oxide (NTG) to improve the photocatalytic efficiency. NTG exhibited high photocatalytic efficiency hydrogen evolution. It was of 716.0 or 112.0  $\mu$ mol h<sup>-1</sup> g<sup>-1</sup> at high pressure Hg or Xe lamp, which was around 9.2 or 13.6 times higher than P25

Recently, gold nanoparticles were reinforced on TiO2-C3N4 for CO oxidation in visible light illumination exploiting hydrothermal method; beginning with titanium glycolate and graphitic C as precursors. TiO2-C3N4 microspheres were prepared and then decorated with gold nanoparticles by letting HAuCl reaction at alkaline pH (pH = 10) in the attendance of sodium carbonate. After 2 h, the dried and washed powder was calcinated at 350 °C.306 Besides, visible light dynamic silver modified titania catalyst was described for the utilization in the decomposition of MeOH, CH<sub>3</sub>COOH, 2-PrOH and Escherichia coli.307 A plasmonic gold silver alloy on TiO2 photocatalyst was also described that indicated elevated degradation of stearic acid at 490 nm than reported using pristine TiO2.308. Qiu et al.309 have described that CuxO/TiO2 photocatalyst resulted into effective VOCs uptake. Furthermore, Wang et al.310 prepared and used TiO2 NRs/FexOy/Ag core shell nanostructures for photodegradation of rhodamine B in solar light illumination. Recently, a reviews described successful removal of benzene, methylene blue and carbamazepine by photodegradation using CNT/TiO2 nanostructured composites.311

### 10. Future challenges and perspectives

Recently, the applications of TiO2 nanostructures have been exploited to clean environment and produce hydrogen. But there are certain limitations, which we have to overcome to make the structures applicable in real life problems. The efficiencies of these structures are not excellent; especially for decomposing of persistent organic volatile pollutants and production of hydrogen at large scale. Generally, doped TiO<sub>2</sub> nanostructures result into poor photoactivity. Other challenges are to augment spectral sensitivity of these structures to visible and NIR regions and the bio-compatibility of TiO<sub>2</sub> nanostructures. Therefore, there is a great need of future research focusing constant photoactivity in the long run. These can be achieved by modifying the synthetic routs. Nonmetal doped TiO<sub>2</sub> nanostructures have low photocatalytic activity under visible light UV radiation. Therefore, some materials such as polymers, glass, ceramics, or metals may serve as magical identities in this area for economic and eco-friendly applications.

Future research needs the development of new synthetic procedures and nanostructures with higher surface states. It may be served by non-lithographic complementary metal oxide semiconductor compatible techniques. This technique may be applicable for new doping materials, dopant incorporation into TiO<sub>2</sub> nanostructures and applications for environmental and alternate energy areas. Besides, visible to near infra-red activated titanium nanostructures should be designed. TiO2 nanostructures may serve as the ideal materials in biological and medicinal science. Therefore, there is a great need to study the bio-compatibility of these structures at supra molecular level. In a nut shell, the researchers have several challenges to tackle with them in near future. Therefore, there is a great need to improve the structures and properties of these materials. The basic knowledge of chemistry, physics and computer modeling may help to achieve the task.

#### 11. Conclusion

An inclusive review of the syntheses, properties and applications of TiO2 nanostructures is offered. These nanostructures can be prepared by different synthesis procedures as per the requirements. It was observed that the physico-chemical properties of titanium dioxide nanostructures are responsible for wide applications in several fields such as gas sensors, white pigments, lithium batteries, photocatalytic applications (photodegradation of organic compounds), photovoltaic applications and water splitting. TiO2 nanostructures play a great role in water purification by degrading biological and organic pollutants. The use in generating hydrogen as a green currency is the biggest asset of nano TiO<sub>2</sub> structures. It was observed that the decomposing and water splitting properties of TiO2 nanostructures are not good enough, which can be exploited at a commercial level economically. It may be predicted that these materials may be the choice in water purification. Most interestingly, we believe that TiO2 nanostructures will achieve a great reputation in generation of hydrogen fuel - a need of the next century.

# Conflicts of interest

There is no conflict of interest.

# References

- 1 G. Pfaff and P. Reynders, Chem. Rev., 1999, 99, 1963-1982.
- 2 A. Salvador, M. C. Pascual-Martí, J. R. Adell, A. Requeni and J. G. March, J. Pharm. Biomed. Anal., 2000, 22, 301-306.
- 3 M. D. Newman, M. Stotland and J. I. Ellis, J. Am. Acad. Dermatol., 2009, 61, 685-692.
- 4 A. Fujishima and K. Honda, *Nature*, 1972, 238, 37-38.
- 5 T. Kaida, K. Kobayashi, M. Adachi and F. Suzuki, J. Cosmet. Sci., 2004, 55, 219-220.
- 6 J. J. Wang, B. J. S. Sanderson and H. Wang, Mutat. Res., Genet. Toxicol. Environ. Mutagen., 2007, 628, 99-106.

**RSC Advances** Review

- 7 R. A. Schwartz, Acta Dermatovenerol. Croat., 2004, 12(4), 249.
- 8 J. J. Jacobs, A. K. Skipor, J. Black, R. M. Urban and J. O. Galante, J. Bone Jt. Surg., Am. Vol., 1991, 73, 1475-1486.
- 9 Y. Sul, Int. J. Nanomed., 2010, 5, 87-100.
- 10 A. Patri, T. Umbreit, J. Zheng, K. Nagashima, P. Goering, S. Francke-Carroll, E. Gordon, J. Weaver, T. Miller, N. Sadrieh, S. McNeil and M. Stratmeyer, J. Appl. Toxicol., 2009, 29, 662-672.
- 11 A. Fujishima, T. N. Rao and D. A. Tryk, J. Photochem. Photobiol., C, 2000, 1, 1-21.
- 12 D. Tryk, A. Fujishima and K. Honda, Electrochim. Acta, 2000, 45, 2363-2376.
- 13 M. Gratzel, J. Sol-Gel Sci. Technol., 2001, 22, 7-13.
- 14 S. Ivanković, M. Gotić, M. Jurin and S. Musić, J. Sol-Gel Sci. Technol., 2003, 27, 225-233.
- 15 A. L. Linsebigler, G. Lu and J. T. Yates, Chem. Rev., 1995, 95, 735-758.
- 16 A. Mills and S. Le Hunte, J. Photochem. Photobiol., A, 1997, 108, 1-35.
- 17 A. P. Alivisatos, *I. Phys. Chem.*, 1996, **100**, 13226–13239.
- 18 A. Hagfeldt and M. Graetzel, Chem. Rev., 1995, 95, 49-68.
- 19 A. P. Alivisatos, Science, 1996, 271, 933-937.
- 20 C. Burda, X. Chen, R. Narayanan and M. A. El-Sayed, Chem. Rev., 2005, 105, 1025-1102.
- 21 C. B. Murray, C. R. Kagan and M. G. Bawendi, Annu. Rev. Mater. Sci., 2000, 30, 545-610.
- 22 Y. Yin and A. P. Alivisatos, Nature, 2005, 437, 664-670.
- 23 D. M. Adams, L. Brus, C. E. D. Chidsey, S. Creager, C. Creutz, C. R. Kagan, P. V. Kamat, M. Lieberman, S. Lindsay, R. A. Marcus, R. M. Metzger, M. E. Michel-Beyerle, J. R. Miller, M. D. Newton, D. R. Rolison, O. Sankey, K. S. Schanze, J. Yardley and X. Zhu, J. Phys. Chem. B, 2003, 107, 6668-6697.
- 24 D. Beydoun, R. Amal, G. Low and S. McEvoy, J. Nanopart. Res., 1999, 1, 439-458.
- 25 X. Chen, Y. Lou, S. Dayal, X. Qiu, R. Krolicki, C. Burda, C. Zhao and J. Becker, J. Nanosci. Nanotechnol., 2005, 5, 1408-1420.
- 26 H. Dai, Acc. Chem. Res., 2002, 35, 1035-1044.
- 27 M. S. Dresselhaus and G. Dresslhaus, Annu. Rev. Mater. Sci., 1995, 25, 487-523.
- 28 M. S. Dresselhaus, G. Dresselhaus, A. Jorio, A. G. Souza Filho, M. A. Pimenta and R. Saito, Acc. Chem. Res., 2002, 35, 1070-1078.
- 29 M. S. Dresselhaus, G. Dresselhaus and A. Jorio, Annu. Rev. Mater. Res., 2004, 34, 247-278.
- 30 A. L. Efros and M. Rosen, Annu. Rev. Mater. Sci., 2000, 30, 475-521.
- 31 M. A. El-Sayed, Acc. Chem. Res., 2004, 37, 326-333.
- 32 M. Gratzel, Prog. Photovoltaics, 2000, 8, 171-185.
- 33 M. R. Hoffmann, S. T. Martin, W. Choi and D. W. Bahnemann, Chem. Rev., 1995, 95, 69-96.
- 34 S. Link and M. A. El-Sayed, Annu. Rev. Phys. Chem., 2003, 54, 331-366.
- 35 S. S. Mao, Int. J. Nanotechnol., 2004, 1, 42.
- 36 M. Nirmal and L. Brus, Acc. Chem. Res., 1999, 32, 407-414.
- 37 A. J. Nozik, Inorg. Chem., 2005, 44, 6893-6899.

- 38 A. J. Nozik, Annu. Rev. Phys. Chem., 2001, 52, 193-231.
- 39 M. Ouyang, J.-L. Huang and C. M. Lieber, Acc. Chem. Res., 2002, 35, 1018-1025.
- 40 L. Vayssieres, Int. J. Nanotechnol., 2004, 1(1-2), 1-41.
- 41 M. Grätzel, J. Photochem. Photobiol., C, 2003, 4, 145-153.
- 42 V. E. Henrich, Rep. Prog. Phys., 1985, 48, 1481-1541.
- 43 J. F. Banfield, B. L. Bischoff and M. A. Anderson, Chem. Geol., 1993, 110, 211-231.
- 44 P. Y. Simons and F. Dachille, Acta Crystallogr., 1967, 23,
- 45 J. Tang and S. Endo, J. Am. Ceram. Soc., 1993, 76, 796-798.
- 46 J. S. Olsen, L. Gerward and J. Jiang, J. Phys. Chem. Solids, 1999, 60, 229-233.
- 47 M. Latroche, L. Brohan, R. Marchand and M. Tournoux, J. Solid State Chem., 1989, 81, 78-82.
- 48 J. Akimoto, Y. Gotoh, Y. Oosawa, N. Nonose, T. Kumagai, K. Aoki and H. Takei, J. Solid State Chem., 1994, 113, 27-36.
- 49 R. Marchand, L. Brohan and M. Tournoux, Mater. Res. Bull., 1980, 15, 1129-1133.
- 50 J. Haines and J. M. Léger, Phys. B, 1993, 192, 233-237.
- 51 M. Horn, C. F. Schwebdtfeger and E. P. Meagher, Z. Kristallogr. Cryst. Mater., 1972, 136, 273-281.
- 52 W. H. Baur, Acta Crystallogr., 1961, 14, 214-216.
- 53 S.-D. Mo and W. Y. Ching, Phys. Rev. B: Condens. Matter Mater. Phys., 1995, 51, 13023-13032.
- 54 J. Pascual, J. Camassel and H. Mathieu, Phys. Rev. B: Condens. Matter Mater. Phys., 1978, 18, 5606-5614.
- 55 A. Eucken and A. Büchner, Z. Phys. Chem., 1934, 27B, 321-
- 56 G. E. Jellison, F. A. Modine and L. A. Boatner, Opt. Lett., 1997, 22, 1808.
- 57 N. Hosaka, T. Sekiya, C. Satoko and S. Kurita, J. Phys. Soc. Jpn, 1997, 66, 877-880.
- 58 D. C. Cronemeyer, Phys. Rev., 1952, 87, 876-886.
- 59 L. Forro, O. Chauvet, D. Emin, L. Zuppiroli, H. Berger and F. Lévy, J. Appl. Phys., 1994, 75, 633-635.
- 60 R. R. Hasiguti and E. Yagi, Phys. Rev. B: Condens. Matter Mater. Phys., 1994, 49, 7251-7256.
- 61 G. A. Acket and J. Volger, Physica, 1966, 32, 1680-1692.
- 62 R. G. Breckenridge and W. R. Hosler, Phys. Rev., 1953, 91, 793-802.
- 63 H. P. R. Frederikse, J. Appl. Phys., 1961, 32, 2211-2215.
- 64 X. Chen and S. S. Mao, Chem. Rev., 2007, 107, 2891-2959.
- 65 T. L. Thompson and J. T. Yates, Chem. Rev., 2006, 106, 4428-
- 66 U. Diebold, Surf. Sci. Rep., 2003, 48, 53-229.
- 67 A. Navrotsky, J. C. Jamieson and O. J. Kleppa, Science, 1967, **158**, 388-389.
- 68 Q. Zhang, Appl. Catal., B, 2000, 26, 207-215.
- 69 L. Thiên-Nga and A. T. Paxton, Phys. Rev. B: Condens. Matter Mater. Phys., 1998, 58, 13233-13241.
- 70 G. Cangiani, Ab-initio Study of the Properties of TiO2 Rutile and Anatase Polytypes, PhD thesis, EPFL - Environmental Chemistry Modeling Laboratory, SISSA, Trieste, Italy, 2003.
- 71 J. Muscat, V. Swamy and N. M. Harrison, Phys. Rev. B: Condens. Matter Mater. Phys., 2002, 65, 224112.

- 72 A. Di Paola, M. Addamo, M. Bellardita, E. Cazzanelli and L. Palmisano, *Thin Solid Films*, 2007, 515, 3527–3529.
- 73 N. Liu, H. G. Steinrück, A. Osvet, Y. Yang and P. Schmuki, *Appl. Phys. Lett.*, 2017, **110**, 072102-1–072102-4.
- 74 J. Jamieson and B. Olinger, Miner Notes, 1969, 54, 1477.
- 75 F. Bregani, C. Casale, L. E. Depero, I. Natali-Sora, D. Robba, L. Sangaletti and G. P. Toledo, *Sens. Actuators, B*, 1996, 31, 25–28.
- 76 M. E. Straumanis, T. Ejima and W. J. James, *Acta Crystallogr.*, 1961, 14, 493–497.
- 77 O. R. S. da Rocha, R. F. Dantas, M. M. M. B. Duarte, M. M. L. Duarte and V. L. da Silva, *Chem. Eng. J.*, 2010, 157, 80–85.
- 78 G. K. Mor, O. K. Varghese, M. Paulose, K. Shankar and C. A. Grimes, Sol. Energy Mater. Sol. Cells, 2006, 90, 2011– 2075.
- 79 Y. Ao, J. Xu, S. Zhang and D. Fu, *Appl. Surf. Sci.*, 2010, **256**, 2754–2758.
- 80 L. Dong, G. Cao, Y. Ma, X. Jia, G. Ye and S. Guan, *Trans. Nonferrous Met. Soc. China*, 2009, **19**, 1583–1587.
- 81 S. Banerjee, J. G. Pal, P. Muraleedharan, A. K. Tyagi and B. Raj, *Res. Commun.*, 2006, **90**, 1378–1383.
- 82 S. Sakthivel and H. Kisch, *Angew. Chem., Int. Ed.*, 2003, 42, 4908–4911.
- 83 H. K. Ardakani, Thin Solid Films, 1994, 248, 234-239.
- 84 A. T. Paxton and L. Thiên-Nga, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1998, **57**, 1579–1584.
- 85 E. C. Akubuiro and X. E. Verykios, *J. Phys. Chem. Solids*, 1989, **50**, 17–26.
- 86 S. Fujitsu and T. Hamada, J. Am. Ceram. Soc., 1994, 77, 3281–3283.
- 87 N. G. Eror, J. Solid State Chem., 1981, 38, 281-287.
- 88 J.-L. Carpentier, A. Lebrun and F. Perdu, *J. Phys. Chem. Solids*, 1989, **50**, 145–151.
- 89 P. Knauth and H. L. Tuller, J. Appl. Phys., 1999, 85, 897-902.
- 90 K. Mizushima, M. Tanaka, A. Asai, S. Iida and J. B. Goodenough, *J. Phys. Chem. Solids*, 1979, **40**, 1129– 1140.
- 91 N. Yu and J. W. Halley, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1995, **51**, 4768–4776.
- 92 H. X. Zhu, P. X. Zhou, X. Li and J.-M. Liu, *Phys. Lett. A*, 2014, 378, 2719–2724.
- 93 F. Arntz and Y. Yacoby, Phys. Rev. Lett., 1966, 17, 857-860.
- 94 A. Frova, P. J. Boddy and Y. S. Chen, *Phys. Rev.*, 1967, **157**, 700–708.
- 95 A. K. Ghosh, F. G. Wakim and R. R. Addiss, *Phys. Rev.*, 1969, 184, 979–988.
- 96 A. Amtout and R. Leonelli, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1995, 51, 6842–6851.
- 97 S. Hüfner and G. K. Wertheim, *Phys. Rev. B: Solid State*, 1973, 7, 2333–2336.
- 98 D. W. Fischer, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1972, 5, 4219–4226.
- 99 F. M. F. de Groot, J. Faber, J. J. M. Michiels, M. T. Czyżyk, M. Abbate and J. C. Fuggle, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1993, 48, 2074–2080.

- 100 L. A. Grunes, Phys. Rev. B: Condens. Matter Mater. Phys., 1983, 27, 2111–2131.
- 101 G. van der Laan, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1990, **41**, 12366–12368.
- 102 F. M. F. de Groot, M. Grioni, J. C. Fuggle, J. Ghijsen, G. A. Sawatzky and H. Petersen, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1989, 40, 5715–5723.
- 103 K. Watanabe, K. Inoue and F. Minami, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1992, **46**, 2024–2033.
- 104 L. Kavan, M. Grätzel, S. E. Gilbert, C. Klemenz and H. J. Scheel, J. Am. Chem. Soc., 1996, 118, 6716–6723.
- 105 J. Park, J. Joo, S. G. Kwon, Y. Jang and T. Hyeon, *Angew. Chem., Int. Ed.*, 2007, **46**, 4630–4660.
- 106 Y. Bessekhouad, D. Robert and J. V. Weber, *J. Photochem. Photobiol.*, A, 2003, 157, 47–53.
- 107 G. Oskam, A. Nellore, R. L. Penn and P. C. Searson, J. Phys. Chem. B, 2003, 107, 1734–1738.
- 108 T. Sugimoto, Adv. Colloid Interface Sci., 1987, 28, 65-108.
- 109 M. A. Anderson, M. J. Gieselmann and Q. Xu, J. Membr. Sci., 1988, 39, 243–258.
- 110 E. A. Barringer and H. K. Bowen, *Langmuir*, 1985, **1**, 414–420.
- 111 J. H. Jean and T. A. Ring, Langmuir, 1986, 2, 251-255.
- 112 C. Kormann, D. W. Bahnemann and M. R. Hoffmann, *J. Phys. Chem.*, 1988, **92**, 5196–5201.
- 113 J. Livage, M. Henry and C. Sanchez, *Prog. Solid State Chem.*, 1988, **18**, 259–341.
- 114 J.-L. Look and C. F. Zukoski, *J. Am. Ceram. Soc.*, 1995, 78, 21–32.
- 115 J. L. Look and C. F. Zukoski, *J. Am. Ceram. Soc.*, 1992, 75, 1587–1595.
- 116 B. O'Regan and M. Grätzel, Nature, 1991, 353, 737-740.
- 117 R. L. Penn and J. F. Banfield, *Geochim. Cosmochim. Acta*, 1999, **63**, 1549–1557.
- 118 D. Vorkapic and T. Matsoukas, *J. Am. Ceram. Soc.*, 2005, **81**, 2815–2820.
- 119 D. Vorkapic and T. Matsoukas, J. Colloid Interface Sci., 1999, 214, 283–291.
- 120 C.-S. Kim, B. K. Moon, J.-H. Park, S. Tae Chung and S.-M. Son, *J. Cryst. Growth*, 2003, **254**, 405–410.
- 121 L. Miao, S. Tanemura, S. Toh, K. Kaneko and M. Tanemura, *J. Cryst. Growth*, 2004, **264**, 246–252.
- 122 M. S. Ghamsari, F. Hajiesmaeilbaigi and S. Mirdamadi, Semicond. Phys., Quantum Electron. Optoelectron., 2007, 10, 36–39.
- 123 Y. Lin, G. S. Wu, X. Y. Yuan, T. Xie and L. D. Zhang, *J. Phys.: Condens. Matter*, 2003, **15**, 2917–2922.
- 124 B. Liu and E. S. Aydil, *J. Am. Chem. Soc.*, 2009, **131**, 3985–3990.
- 125 T. Kasuga, M. Hiramatsu, A. Hoson, T. Sekino and K. Niihara, *Langmuir*, 1998, **14**, 3160–3163.
- 126 T. Kasuga, M. Hiramatsu, A. Hoson, T. Sekino and K. Niihara, *Adv. Mater.*, 1999, **11**, 1307–1311.
- 127 F. Sayilkan, Turk. J. Chem., 2007, 31, 211-221.
- 128 S. Y. Chae, M. K. Park, S. K. Lee, T. Y. Kim, S. K. Kim and W. I. Lee, *Chem. Mater.*, 2003, **15**, 3326–3331.

129 F. Cot, A. Larbot, G. Nabias and L. Cot, *J. Eur. Ceram. Soc.*, 1998, **18**, 2175–2181.

**RSC Advances** 

- 130 J. Yang, S. Mei and J. M. F. Ferreira, *J. Colloid Interface Sci.*, 2003, **260**, 82–88.
- 131 J. Yang, S. Mei and J. M. F. Ferreira, *Mater. Sci. Eng.*, C, 2001, 15, 183–185.
- 132 J. Yang, S. Mei and J. M. F. Ferreira, *J. Mater. Res.*, 2002, 17, 2197–2200.
- 133 M. Rehan, X. Lai and G. M. Kale, *CrystEngComm*, 2011, 13, 3725.
- 134 R. Vijayalakshmi and V. Rajendran, *Scholars Research Library*, 2012, 4, 1183–1190.
- 135 Y. X. Zhang, G. H. Li, Y. X. Jin, Y. Zhang, J. Zhang and L. D. Zhang, *Chem. Phys. Lett.*, 2002, **365**, 300–304.
- 136 T. Kasuga, M. Hiramatsu, A. Hoson, T. Sekino and K. Niihara, *Adv. Mater.*, 1999, **11**, 1307–1311.
- 137 Z. Liu, Y. G. Andreev, A. Robert Armstrong, S. Brutti, Y. Ren and P. G. Bruce, *Prog. Nat. Sci.: Mater. Int.*, 2013, 23, 235–244
- 138 M. Cargnello, T. R. Gordon and C. B. Murray, *Chem. Rev.*, 2014, **114**, 9319–9345.
- 139 A. Craig and K. Gopal, *TiO*<sub>2</sub> *Nanotube Arrays, Synthesis, properties and Application*, Springer, Dordrecht Heidelberg, London, New York, 2009.
- 140 D. Gong, C. A. Grimes, O. K. Varghese, W. Hu, R. S. Singh, Z. Chen and E. C. Dickey, *J. Mater. Res.*, 2001, **16**, 3331– 3334.
- 141 G. K. Mor, O. K. Varghese, M. Paulose and C. A. Grimes, Sens. Lett., 2003, 1, 42–46.
- 142 Q. Cai, M. Paulose, O. K. Varghese and C. A. Grimes, *J. Mater. Res.*, 2005, **20**, 230–236.
- 143 G. K. Mor, K. Shankar, O. K. Varghese and C. A. Grimes, *J. Mater. Res.*, 2004, 19, 2989–2996.
- 144 V. Zwilling, M. Aucouturier and E. Darque-Ceretti, *Electrochim. Acta*, 1999, 45, 921–929.
- 145 Y. Shimizu, N. Kuwano, T. Hyodo and M. Egashira, Sens. Actuators, B, 2002, 83, 195-201.
- 146 J. Yamamoto, A. Tan, R. Shiratsuchi, S. Hayase, C. R. Chenthamarakshan and K. Rajeshwar, *Adv. Mater.*, 2003, **15**, 1823–1825.
- 147 G. Patermarakis, J. Electrochem. Soc., 1995, 142, 737.
- 148 K. Shankar, G. K. Mor, A. Fitzgerald and C. A. Grimes, *J. Phys. Chem. C*, 2007, **111**, 21–26.
- 149 C. Ruan, M. Paulose, O. K. Varghese and C. A. Grimes, *Sol. Energy Mater. Sol. Cells*, 2006, **90**, 1283–1295.
- 150 M. Paulose, K. Shankar, S. Yoriya, H. E. Prakasam, O. K. Varghese, G. K. Mor, T. A. Latempa, A. Fitzgerald and C. A. Grimes, J. Phys. Chem. B, 2006, 110, 16179–16184.
- 151 S. Yoriya, G. K. Mor, S. Sharma and C. A. Grimes, *J. Mater. Chem.*, 2008, **18**, 3332.
- 152 R. Subasri, M. Tripathi, K. Murugan, J. Revathi, G. V. N. Rao and T. N. Rao, *Mater. Chem. Phys.*, 2010, **124**, 63–68.
- 153 Y. Yin, Z. Jin, F. Hou and X. Wang, *J. Am. Ceram. Soc.*, 2007, **90**, 2384–2389.
- 154 G. K. Mor, O. K. Varghese, M. Paulose, N. Mukherjee and C. A. Grimes, *J. Mater. Res.*, 2003, **18**, 2588–2593.

- 155 G. K. Mor, M. A. Carvalho, O. K. Varghese, M. V. Pishko and C. A. Grimes, J. Mater. Res., 2004, 19, 628–634.
- 156 G. K. Mor, K. Shankar, M. Paulose, O. K. Varghese and C. A. Grimes, *Nano Lett.*, 2005, 5, 191–195.
- 157 O. K. Varghese, D. Gong, M. Paulose, C. A. Grimes and E. C. Dickey, *J. Mater. Res.*, 2003, **18**, 156–165.
- 158 S. Bauer, S. Kleber and P. Schmuki, *Electrochem. Commun.*, 2006, **8**, 1321–1325.
- 159 O. K. Varghese, D. Gong, M. Paulose, K. G. Ong, E. C. Dickey and C. A. Grimes, *Adv. Mater.*, 2003, **15**, 624–627.
- 160 L. K. Preethi, T. Mathews, M. Nand, S. N. Jha, C. S. Gopinath and S. Dash, *Appl. Catal.*, *B*, 2017, **218**, 9–19.
- 161 S. Seifried, M. Winterer and H. Hahn, *Chem. Vap. Deposition*, 2000, **6**, 239–244.
- 162 J. A. Ayllón, A. Figueras, S. Garelik, L. Spirkova, J. Durand and L. Cot, *J. Mater. Sci. Lett.*, 1999, **18**, 1319–1321.
- 163 S. K. Pradhan, P. J. Reucroft, F. Yang and A. Dozier, *J. Cryst. Growth*, 2003, **256**, 83–88.
- 164 K. Okuyama, Y. Kousaka, N. Tohge, S. Yamamoto, J. J. Wu, R. C. Flagan and J. H. Seinfeld, *AIChE J.*, 1986, 32, 2010– 2019.
- 165 K. Okuyama, R. Ushio, Y. Kousaka, R. C. Flagan and J. H. Seinfeld, *AIChE J.*, 1990, 36, 409–419.
- 166 K. Okuyama, J.-T. Jeung, Y. Kousaka, H. V. Nguyen, J. J. Wu and R. C. Flagan, *Chem. Eng. Sci.*, 1989, 44, 1369–1375.
- 167 Z. Ding, X. Hu, G. Q. Lu, P.-L. Yue and P. F. Greenfield, *Langmuir*, 2000, **16**, 6216–6222.
- 168 J.-J. Wu and C.-C. Yu, *J. Phys. Chem. B*, 2004, **108**, 3377–3379.
- 169 D. G. Park and J. M. Burlitch, *Chem. Mater.*, 1992, 4, 500-502.
- 170 H. D. Jang and S.-K. Kim, *Mater. Res. Bull.*, 2001, **36**, 627–637.
- 171 Y.-L. Li and T. Ishigaki, Thin Solid Films, 2002, 407, 79-85.
- 172 S.-M. Oh and T. Ishigaki, *Thin Solid Films*, 2004, **457**, 186–191.
- 173 X. H. Wang, J.-G. Li, H. Kamiyama, M. Katada, N. Ohashi, Y. Moriyoshi and T. Ishigaki, *J. Am. Chem. Soc.*, 2005, **127**, 10982–10990.
- 174 M. Grujić-Brojčin, M. J. Šćepanović, Z. D. Dohčević-Mitrovi, I. Hinić, B. Matović, G. Stanišić and Z. V Popović, *J. Phys. D: Appl. Phys.*, 2005, **38**, 1415–1420.
- 175 M. Šćepanović, Z. Dohčević-Mitrović, I. Hinić, M. Grujić-Brojčin, G. Stanišić and Z. V. Popović, *Mater. Sci. Forum*, 2005, **494**, 265–270.
- 176 J.-M. Wu, H. C. Shih and W.-T. Wu, *Chem. Phys. Lett.*, 2005, 413, 490-494.
- 177 J.-M. Wu, H. C. Shih, W.-T. Wu, Y.-K. Tseng and I.-C. Chen, *J. Cryst. Growth*, 2005, **281**, 384–390.
- 178 B. Xiang, Y. Zhang, Z. Wang, X. H. Luo, Y. W. Zhu, H. Z. Zhang and D. P. Yu, *J. Phys. D: Appl. Phys.*, 2005, **38**, 1152–1155.
- 179 H. Zhang, X. Luo, J. Xu, B. Xiang and D. Yu, *J. Phys. Chem. B*, 2004, **108**, 14866–14869.
- 180 J.-M. Wu, H. C. Shih and W.-T. Wu, *Nanotechnology*, 2006, 17, 105–109.

Review

181 D. K. Hwang, J. H. Moon, Y. G. Shul, K. T. Jung, D. H. Kim and D. W. Lee, *J. Sol-Gel Sci. Technol.*, 2003, **26**, 783–787.

- 182 J.-W. Kim, J.-W. Shim, J.-H. Bae, S.-H. Han, H.-K. Kim, I.-S. Chang, H.-H. Kang and K.-D. Suh, *Colloid Polym. Sci.*, 2002, **280**, 584–588.
- 183 B. Mahltig, H. Böttcher, K. Rauch, U. Dieckmann, R. Nitsche and T. Fritz, *Thin Solid Films*, 2005, **485**, 108–114.
- 184 A. P. Popov, A. V Priezzhev, J. Lademann and R. Myllylä, *J. Phys. D: Appl. Phys.*, 2005, **38**, 2564–2570.
- 185 C. E. Sittig, Charakterisierung der Oxidschichten auf Titan und Titanlegierungen sowie deren Reaktionen in Kontact mit biologisch relevanten Modellösungen, PhD thesis, ETH Nr, 12657, Zürich, 1998.
- 186 W. Clark and P. Broadhead, *J. Phys. C: Solid State Phys.*, 1970, 3, 1047.
- 187 R. Wang, K. Hashimoto, A. Fujishima, M. Chikuni, E. Kojima, A. Kitamura, M. Shimohigoshi and T. Watanabe, *Nature*, 1997, **388**, 431–432.
- 188 A. Fujishima, X. Zhang and D. Tryk, *Surf. Sci. Rep.*, 2008, **63**, 515–582.
- 189 Y. Xie, Electrochim. Acta, 2006, 51, 3399-3406.
- 190 Y. Lai, L. Sun, Y. Chen, H. Zhuang, C. Lin and J. W. Chin, *J. Electrochem. Soc.*, 2006, **153**, D123.
- 191 N. M. Mahmoodi, M. Arami, N. Y. Limaee and N. S. Tabrizi, *Chem. Eng. J.*, 2005, **112**, 191–196.
- 192 A.-P. Zhang, World J. Gastroenterol., 2004, 10, 3191-3193.
- 193 A. O. Ibhadon, Multifunctional TiO<sub>2</sub> Catalysis and Applications, in *Proceedings of Green Chemistry and Engineering International Conference*, Washington, DC, USA, 24–26 June 2008.
- 194 C.-C. Wang, Z. Zhang and J. Y. Ying, *Nanostruct. Mater.*, 1997, **9**, 583–586.
- 195 J.-M. Wu, T.-W. Zhang, Y.-W. Zeng, S. Hayakawa, K. Tsuru and A. Osaka, *Langmuir*, 2005, **21**, 6995–7002.
- 196 T. Peng, D. Zhao, K. Dai, W. Shi and K. Hirao, *J. Phys. Chem. B*, 2005, **109**, 4947–4952.
- 197 S. Yang, X. Quan, X. Li, N. Fang, N. Zhang and H. Zhao, *J. Environ. Sci.*, 2005, **17**, 290–293.
- 198 Y. Bessekhouad, D. Robert, J.-V. Weber and N. Chaoui, *J. Photochem. Photobiol.*, A, 2004, **167**, 49–57.
- 199 Y. Cao, W. Yang, W. Zhang, G. Liu and P. Yue, *New J. Chem.*, 2004, **28**, 218.
- 200 W. Li, Y. Wang, H. Lin, S. Ismat Shah, C. P. Huang, D. J. Doren, S. A. Rykov, J. G. Chen and M. A. Barteau, *Appl. Phys. Lett.*, 2003, 83, 4143–4145.
- 201 S. Peng, Y. Li, F. Jiang, G. Lu and S. Li, *Chem. Phys. Lett.*, 2004, **398**, 235–239.
- 202 Y. Sakatani, H. Ando, K. Okusako, H. Koike, J. Nunoshige, T. Takata, J. N. Kondo, M. Hara and K. Domen, *J. Mater. Res.*, 2004, **19**, 2100–2108.
- 203 X. Zhang and L. Lei, Mater. Lett., 2008, 62, 895-897.
- 204 M. S. Nahar, K. Hasegawa and S. Kagaya, *Chemosphere*, 2006, **65**, 1976–1982.
- 205 K. Iketani, R.-D. Sun, M. Toki, K. Hirota and O. Yamaguchi, *Mater. Sci. Eng., B*, 2004, **108**, 187–193.
- 206 J. Zhu, F. Chen, J. Zhang, H. Chen and M. Anpo, *J. Photochem. Photobiol.*, *A*, 2006, **180**, 196–204.

- 207 D. Hyun Kim, K. Sub Lee, Y.-S. Kim, Y.-C. Chung and S.-J. Kim, *J. Am. Ceram. Soc.*, 2006, **89**, 515–518.
- 208 J. C.-S. Wu and C.-H. Chen, *J. Photochem. Photobiol.*, *A*, 2004, **163**, 509–515.
- 209 C.-C. Pan and J. C. S. Wu, Mater. Chem. Phys., 2006, 100, 102–107.
- 210 S. Kim, S.-J. Hwang and W. Choi, *J. Phys. Chem. B*, 2005, **109**, 24260–24267.
- 211 R. Amadelli, L. Samiolo, A. Maldotti, A. Molinari, M. Valigi and D. Gazzoli, *Int. J. Photoenergy*, 2008, **2008**, 1–9.
- 212 T. Lindgren, J. M. Mwabora, E. Avendaño, J. Jonsson, A. Hoel, C.-G. Granqvist and S.-E. Lindquist, *J. Phys. Chem. B*, 2003, **107**, 5709–5716.
- 213 C. Burda, Y. Lou, X. Chen, A. C. S. Samia, J. Stout and J. L. Gole, *Nano Lett.*, 2003, 3, 1049–1051.
- 214 X. Chen, Y.-B. Lou, A. C. S. Samia, C. Burda and J. L. Gole, *Adv. Funct. Mater.*, 2005, **15**, 41–49.
- 215 Y. Choi, T. Umebayashi and M. Yoshikawa, J. Mater. Sci., 2004, 39, 1837–1839.
- 216 H. Irie, Y. Watanabe and K. Hashimoto, *Chem. Lett.*, 2003, **32**, 772–773.
- 217 Y. Xie, L. M. Zhou and H. Huang, *Mater. Lett.*, 2006, **60**, 3558–3560.
- 218 S. Sakthivel, M. Janczarek and H. Kisch, *J. Phys. Chem. B*, 2004, **108**, 19384–19387.
- 219 H. Tokudome and M. Miyauchi, *Chem. Lett.*, 2004, **33**, 1108–1109.
- 220 C. Shifu, C. Lei, G. Shen and C. Gengyu, *Chem. Phys. Lett.*, 2005, **413**, 404–409.
- 221 O. Diwald, T. L. Thompson, T. Zubkov, S. D. Walck and J. T. Yates, *J. Phys. Chem. B*, 2004, **108**, 6004–6008.
- 222 T. Ohno, M. Akiyoshi, T. Umebayashi, K. Asai, T. Mitsui and M. Matsumura, *Appl. Catal.*, *A*, 2004, 265, 115–121.
- 223 M. Shen, Z. Wu, H. Huang, Y. Du, Z. Zou and P. Yang, *Mater. Lett.*, 2006, **60**, 693–697.
- 224 J. C. Yu, J. Yu, W. Ho, Z. Jiang and L. Zhang, *Chem. Mater.*, 2002, 14, 3808–3816.
- 225 D. Li, H. Haneda, N. K. Labhsetwar, S. Hishita and N. Ohashi, *Chem. Phys. Lett.*, 2005, **401**, 579–584.
- 226 D. Li, H. Haneda, S. Hishita, N. Ohashi and N. K. Labhsetwar, *J. Fluorine Chem.*, 2005, **126**, 69–77.
- 227 M. Grätzel, Nature, 2001, 414, 338-344.
- 228 F. Cao, G. Oskam, G. J. Meyer and P. C. Searson, *J. Phys. Chem.*, 1996, **100**, 17021–17027.
- 229 A. Solbrand, H. Lindström, H. Rensmo, A. Hagfeldt, S.-E. Lindquist and S. Södergren, *J. Phys. Chem. B*, 1997, **101**, 2514–2518.
- 230 M. Ni, M. K. H. Leung, D. Y. C. Leung and K. Sumathy, Renewable Sustainable Energy Rev., 2007, 11, 401–425.
- 231 A. Kudo and Y. Miseki, Chem. Soc. Rev., 2009, 38, 253-278.
- 232 A. Hameed and M. A. Gondal, *J. Mol. Catal. A: Chem.*, 2004, **219**, 109–119.
- 233 A. Yamakata, T. Ishibashi and H. Onishi, *J. Mol. Catal. A: Chem.*, 2003, **199**, 85–94.
- 234 W. Y. Teoh, J. A. Scott and R. Amal, *J. Phys. Chem. Lett.*, 2012, 3, 629–639.

235 M. S. Wrighton, A. B. Ellis, P. T. Wolczanski, D. L. Morse, H. B. Abrahamson and D. S. Ginley, *J. Am. Chem. Soc.*, 1976, 98, 2774–2779.

236 Z.-L. Jin and G.-X. Lu, Energy Fuels, 2005, 19, 1126-1132.

**RSC Advances** 

- 237 S. U. M. Khan, M. Al-Shahry and W. B. Ingler, *Science*, 2002, 297, 2243–2245.
- 238 M. Matsuoka, M. Kitano, M. Takeuchi, M. Anpo and J. M. Thomas, *Top. Catal.*, 2005, **35**, 305–310.
- 239 M. Matsuoka, M. Kitano, M. Takeuchi, M. Anpo and J. M. Thomas, *Mater. Sci. Forum*, 2005, **486–487**, 81–84.
- 240 D. Bocharov, S. Piskunov, Y. F. Zhukovskii, E. Spohr and P. N. D'yachkov, *Vacuum*, 2017, **146**, 562–569.
- 241 J. F. Guayaquil-Sosa, B. Serrano-Rosales, P. J. Valadés-Pelayo and H. de Lasa, *Appl. Catal.*, *B*, 2017, 211, 337–348.
- 242 M. Alitabar and H. Yoozbashizadeh, *Mater. Res. Bull.*, 2017, 95, 169–176.
- 243 K. Dhanalakshmi, *Int. J. Hydrogen Energy*, 2001, **26**, 669-674.
- 244 R. Argazzi, N. Y. Murakami Iha, H. Zabri, F. Odobel and C. A. Bignozzi, *Coord. Chem. Rev.*, 2004, 248, 1299–1316.
- 245 A. S. Polo, M. K. Itokazu and N. Y. Murakami Iha, *Coord. Chem. Rev.*, 2004, 248, 1343–1361.
- 246 D. Duonghong, E. Borgarello and M. Graetzel, *J. Am. Chem. Soc.*, 1981, **103**, 4685–4690.
- 247 T. Sreethawong, C. Junbua and S. Chavadej, *J. Power Sources*, 2009, **190**, 513–524.
- 248 Y. Li, C. Xie, S. Peng, G. Lu and S. Li, *J. Mol. Catal. A: Chem.*, 2008, **282**, 117–123.
- 249 K. K. Mandari, B. S. Kwak, A. K. R. Police and M. Kang, *Mater. Res. Bull.*, 2017, **95**, 515–524.
- 250 H. Zhang, F. Liu, H. Wu, X. Cao, J. Sun and W. Lei, *RSC Adv.*, 2017, 7, 40327–40333.
- 251 B. Hou, L. Shen, H. Shi, R. Kapadia and S. B. Cronin, *Phys. Chem. Chem. Phys.*, 2017, **19**, 2877–2881.
- 252 J. Zhang, Z. Yu, Z. Gao, H. Ge, S. Zhao, C. Chen, S. Chen, X. Tong, M. Wang, Z. Zheng and Y. Qin, *Angew. Chem., Int. Ed.*, 2017, 56, 816–820.
- 253 H. Xu, S. Li, L. Ge, C. Han, Y. Gao and D. Dai, *Int. J. Hydrogen Energy*, 2017, **42**, 22877–22886.
- 254 Y. Sui, S. Liu, T. Li, Q. Liu, T. Jiang, Y. Guo and J.-L. Luo, *J. Catal.*, 2017, 353, 250–255.
- 255 J. Si, Y. Wang, X. Xia, S. Peng, Y. Wang, S. Xiao, L. Zhu, Y. Bao, Z. Huang and Y. Gao, *J. Power Sources*, 2017, **360**, 353–359.
- 256 M. Wang, Z. Li, Y. Wu, J. Ma and G. Lu, *J. Catal.*, 2017, 353, 162–170.
- 257 R. Liu, Z. Sun, X. Song, Y. Zhang, L. Xu and L. Xi, *Appl. Catal.*, *A*, 2017, 544, 137–144.
- 258 P. V Kamat and D. Meisel, *Curr. Opin. Colloid Interface Sci.*, 2002, 7, 282–287.
- 259 W. Choi, J. Lee, S. Kim, S. Hwang, M. C. Lee and T. K. Lee, *J. Ind. Eng. Chem.*, 2003, **9**, 96–101.
- 260 H. Hussain, G. Tocci, T. Woolcot, X. Torrelles, C. L. Pang, D. S. Humphrey, C. M. Yim, D. C. Grinter, G. Cabailh, O. Bikondoa, R. Lindsay, J. Zegenhagen, A. Michaelides and G. Thornton, *Nat. Mater.*, 2017, 16(4), 461–466.
- 261 P. Salvador, New J. Chem., 1988, 12, 35-43.

- 262 E. Liu, L. Kang, Y. Yang, T. Sun, X. Hu, C. Zhu, H. Liu, Q. Wang, X. Li and J. Fan, *Nanotechnology*, 2014, 25, 165401.
- 263 K. Nishijima, T. Kamai, N. Murakami, T. Tsubota and T. Ohno, *Int. J. Photoenergy*, 2008, **2008**, 1–7.
- 264 Y.-S. Chen and P. V. Kamat, *J. Am. Chem. Soc.*, 2014, **136**, 6075–6082.
- 265 Z. Yang, D. Choi, S. Kerisit, K. M. Rosso, D. Wang, J. Zhang, G. Graff and J. Liu, J. Power Sources, 2009, 192, 588–598.
- 266 P. G. Bruce, B. Scrosati and J.-M. Tarascon, Angew. Chem., Int. Ed., 2008, 47, 2930–2946.
- 267 A. S. Aricò, P. Bruce, B. Scrosati, J.-M. Tarascon and W. van Schalkwijk, *Nat. Mater.*, 2005, **4**, 366–377.
- 268 D. Panduwinata and J. D. Gale, J. Mater. Chem., 2009, 19, 3931–3940.
- 269 C. Arrouvel, S. C. Parker and M. S. Islam, *Chem. Mater.*, 2009, **21**, 4778–4783.
- 270 C.-C. Tsai and H. Teng, Chem. Mater., 2006, 18, 367-373.
- 271 H. Miyazaki, T. Hyodo, Y. Shimizu and M. Egashira, *Sens. Actuators, B*, 2005, **108**, 467–472.
- 272 A. M. Ruiz, A. Cornet and J. R. Morante, *Sens. Actuators, B*, 2004, **100**, 256–260.
- 273 S. El-Sherbiny, F. Morsy, M. Samir and O. A. Fouad, *Appl. Nanosci.*, 2014, 4, 305–313.
- 274 R. I Bickley, T. Gonzalezcarreno, J. S. Lees, L. Palmisano and R. J. D. Tilley, *J. Solid State Chem.*, 1991, 92, 178–190.
- 275 R. Comparelli, E. Fanizza, M. L. Curri, P. D. Cozzoli, G. Mascolo, R. Passino and A. Agostiano, *Appl. Catal., B*, 2005, **55**, 81–91.
- 276 X. Chen and S. S. Mao, Chem. Rev., 2007, 107, 2891-2959.
- 277 M. Pelaez, N. T. Nolan, S. C. Pillai, M. K. Seery, P. Falaras, A. G. Kontos, P. S. M. Dunlop, J. W. J. Hamilton, J. A. Byrne, K. O'Shea, *et al.*, *Appl. Catal.*, *B*, 2012, **125**, 331–349.
- 278 M. Long, L. Zheng, B. Tan and H. Shu, *Appl. Surf. Sci.*, 2016, **386**, 434–441.
- 279 Y. Ben-Shahar and U. Banin, *Top. Curr. Chem.*, 2016, 374, 54.
- 280 S. Murgolo, F. Petronella, R. Ciannarella, R. Comparelli, A. Agostiano, M. L. Curri and G. Mascolo, *Catal. Today*, 2015, **240**, 114–124.
- 281 Y. Tang, G. Zhang, C. Liu, S. Luo, X. Xu, L. Chen and B. Wang, *J. Hazard. Mater.*, 2013, **252–253**, 115–122.
- 282 F. Petronella, A. Truppi, C. Ingrosso, T. Placido, M. Striccoli, M. L. Curri, A. Agostiano and R. Comparelli, *Catal. Today*, 2017, **281**, 85–100.
- 283 L. Karimi, M. E. Yazdanshenas, R. Khajavi, A. Rashidi and M. Mirjalili, *Cellulose*, 2014, **21**, 3813–3827.
- 284 F. Petronella, A. Truppi, T. Sibillano, C. Giannini, M. Striccoli, R. Comparelli and M. L. Curri, *Catalysts*, 2017, 7, 100.
- 285 L. Carbone and P. D. Cozzoli, *Nano Today*, 2010, 5, 449–493.
- 286 Á. Kmetykó, Á. Szániel, C. Tsakiroglou, A. Dombi and K. Hernádi, *React. Kinet., Mech. Catal.*, 2016, 117, 379–390.
- 287 R. Su, R. Tiruvalam, Q. He, N. Dimitratos, L. Kesavan, C. Hammond, J. A. Lopez-Sanchez, R. Bechstein, C. J. Kiely, G. J. Hutchings, et al., ACS Nano, 2012, 6, 6284–6292.

Review

288 A. Takai and P. V. Kamat, ACS Nano, 2011, 5, 7369-7376.

- 289 L. Francioso, D. S. Presicce, P. Siciliano and A. Ficarella, *Sens. Actuators, B*, 2007, **123**, 516–521.
- 290 Y. Mizukoshi, Y. Makise, T. Shuto, J. Hu, A. Tominaga, S. Shironita and S. Tanabe, *Ultrason. Sonochem.*, 2007, **14**, 387–392.
- 291 H. Wang, T. You, W. Shi, J. Li and L. Guo, *J. Phys. Chem. C*, 2012, **116**, 6490–6494.
- 292 R. S. Sonawane and M. K. Dongare, *J. Mol. Catal. A: Chem.*, 2006, **243**, 68–76.
- 293 G. L. Chiarello, E. Selli and L. Forni, *Appl. Catal.*, *B*, 2008, 84, 332–339.
- 294 F. Wenqing, L. Qinghua, Z. Qinghong and W. Ye, *J. Phys. Chem. C*, 2011, **115**, 10694–10701.
- 295 J. Deepa, M. S. Christopher, S. R. Sadhana, M. S. Khadga and J. K. Kenneth, *Int. J. Photoenergy*, 2013, **2013**, 10.
- 296 G. Anna and W. Jerzy, Energy Fuels, 2005, 3, 1143-1147.
- 297 V. I. Yatskiv, A. V. Korzhak, V. M. Granchak, A. S. Kovalenko and S. Ya. Kuchmiy, *Theor. Exp. Chem.*, 2003, 39, 167–171.
- 298 Š. Václav and K. Daniela, Int. J. Photoenergy, 2011, 2011, 14.
- 299 X. Quanjun, Y. Jiaguo and J. Mietek, J. Am. Chem. Soc., 2012, 15, 6575–6578.
- 300 V. K. Anna, I. E. Natalia, L. S. Alexander, K. B. Viktor, E. R. Alexandra, I. L. Valentina, Y. Stepan, V. G. I. Kuchmiy and A. M. Piotr, *J. Photochem. Photobiol.*, A, 2008, 198, 126–134.
- 301 D. Ke, P. Tianyou, Ke. Dingning and W. Bingqing, *Nanotechnology*, 2009, **20**, 12.
- 302 M. Takuya, K. Satoshi, K. Hideyuki, S. Tohru, O. Kiyohisa, C. V. Suresh and S. Kunihiro, *Int. J. Hydrogen Energy*, 2010, 35, 6554–6560.
- 303 R. Nitish, T. L. Kam and P. Debabrata, *J. Phys. Chem. C*, 2015, **33**, 19117–19125.
- 304 Z. Lu, T. Baozhu, C. Feng and Z. Jinlong, *Int. J. Hydrogen Energy*, 2012, **37**, 17060–17067.
- 305 P. Fuyun, L. Yingliang, X. Shengang, L. Jing, W. Chenxu and C. Shaokui, *Int. J. Hydrogen Energy*, 2013, **38**, 2670–2677.
- 306 K. Yang, C. Meng, L. Lin, X. Peng, X. Chen, X. Wang, W. Dai and X. Fu, *Catal. Sci. Technol.*, 2016, **6**, 829–839.
- 307 E. Kowalska, Z. Wei, B. Karabiyik, A. Herissan, M. Janczarek, M. Endo, A. Markowska-Szczupak, H. Remita and B. Ohtani, *Catal. Today*, 2015, **252**, 136–142.
- 308 S. W. Verbruggen, M. Keulemans, M. Filippousi, D. Flahaut, G. van Tendeloo, S. Lacombe, J. A. Martens and S. Lenaerts, *Appl. Catal.*, *B*, 2014, **156–157**, 116–121.
- 309 X. Qiu, M. Miyauchi, K. Sunada, M. Minoshima, M. Liu, Y. Lu, D. Li, Y. Shimodaira, Y. Hosogi and Y. Kuroda, *ACS Nano*, 2012, **6**, 1609–1618.
- 310 Y. Wang, F. Pan, W. Dong, L. Xu, K. Wu, G. Xu and W. Chen, *Appl. Catal.*, *B*, 2016, **189**, 192–198.
- 311 S. Mallakpour and E. Khadem, *Chem. Eng. J.*, 2016, **302**, 344–367.
- 312 M. Horn, C. F. Schwerdtfeger and E. P. Meagher, *Z. Kristallogr.*, 1972, **136**, 273–281.
- 313 H. Tang, Electronic Properties of Anatase TiO<sub>2</sub> Investigated by Electrical and Optical Measurements on Single Crystals and

- *Thin Films*, Département de physique, Ecole polytechnique fédérale de Lausanne EPFL, Lausanne, France, 1994.
- 314 N. Tsuda, K. Nasu, A. Yanase and K. Siratori, *Electronic Conduction in Oxides*, Springer-Verlag, Berlin, Gerseveral, 1991.
- 315 A. Eucken and W. Dannöhl, Die thermisce Ausdehnung einiger Alkalihalogenide and Metalle bei hohen Temperaturen, *Z. Elektrochem.*, 1934, **40**, 814–821.
- 316 M. S. Lee, S.-S. Hong and M. Mohseni, *J. Mol. Catal. A: Chem.*, 2005, 242, 135–140.
- 317 J. O. Carneiro, V. Teixeira, A. Portinha, L. Dupák, A. Magalhães and P. Coutinho, *Vacuum*, 2005, 78, 37–46.
- 318 J. C.-S. Wu and C.-H. Chen, *J. Photochem. Photobiol.*, *A*, 2004, **163**, 509–515.
- 319 X. Z. Li and F. B. Li, Environ. Sci. Technol., 2001, 35, 2381-2387
- 320 F. B. Li and X. Z. Li, Chemosphere, 2002, 48, 1103-1111.
- 321 Z. Wu, F. Dong, W. Zhao and S. Guo, *J. Hazard. Mater.*, 2008, 157, 57–63.
- 322 R. Asahi, Science, 2001, 293, 269-271.
- 323 K. Takeshita, A. Yamakata, T. Ishibashi, H. Onishi, K. Nishijima and T. Ohno, *J. Photochem. Photobiol., A*, 2006, 177, 269–275.
- 324 J. Yu, M. Zhou, B. Cheng and X. Zhao, *J. Mol. Catal. A: Chem.*, 2006, **246**, 176–184.
- 325 S. Y. Treschev, P.-W. Chou, Y.-H. Tseng, J.-B. Wang, E. V. Perevedentseva and C.-L. Cheng, *Appl. Catal., B*, 2008, **79**, 8–16.
- 326 C. Lettmann, K. Hildenbrand, H. Kisch, W. Macyk and W. F. Maier, *Appl. Catal.*, *B*, 2001, **32**, 215–227.
- 327 A. Zaleska, J. W. Sobczak, E. Grabowska and J. Hupka, *Appl. Catal.*, *B*, 2008, **78**, 92–100.
- 328 L. Kőrösi and I. Dékány, *Colloids Surf.*, A, 2006, **280**, 146–154.
- 329 K. Sayama and H. Arakawa, *J. Chem. Soc., Faraday Trans.*, 1997, **93**, 1647–1654.
- 330 K. Sayama and H. Arakawa, J. Phys. Chem., 1993, 97, 531-
- 331 A. Kudo, H. Kato and S. Nakagawa, *J. Phys. Chem. B*, 2000, **104**, 571–575.
- 332 H. Kato and A. Kudo, Chem. Phys. Lett., 1998, 295, 487-492.
- 333 K. Sayama, H. Arakawa and K. Domen, *Catal. Today*, 1996, 28, 175–182.
- 334 K. Fujihara, T. Ohno and M. Matsumura, *J. Chem. Soc., Faraday Trans.*, 1998, **94**, 3705–3709.
- 335 R. Abe, T. Takata, H. Sugihara and K. Domen, *Chem. Commun.*, 2005, 3829–3931.
- 336 M. Higashi, R. Abe, T. Takata and K. Domen, *Chem. Mater.*, 2009, **21**, 1543–1549.
- 337 H. Kato, M. Hori, R. Konta, Y. Shimodaira and A. Kudo, *Chem. Lett.*, 2004, 33, 1348–1349.
- 338 L. B. Fen, T. K. Han, M. Nee, B. C. Ang and M. R. Johan, *Appl. Surf. Sci.*, 2011, **258**, 431–435.