

Cite this: *RSC Adv.*, 2018, 8, 39902

Enhanced performance of chemical looping combustion of methane with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carrier

Hsuan-Chih Wu  and Young Ku*

Iron-based oxygen carriers supported on alumina or alumina/titania were prepared and evaluated for chemical looping combustion of methane. The reduction conversion of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ particles was markedly increased with increasing inlet concentration and was slightly enhanced by elevated operating temperatures. According to the shrinking core model, the mass transfer coefficients (k_g) of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ reduction with methane are found to be 0.07 and 0.12 mm s^{-1} . Complete combustion of methane is almost achieved for experiments conducted with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ operated as the $\text{Fe}_2\text{O}_3/\text{CH}_4$ molar ratio reached about 5.4 and 4.4, respectively. Carbon deposition during methane combustion was avoided by using $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ as an oxygen carrier. More heat was generated for the combustion of methane by $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers because methane more fully reacted with the Fe_2O_3 contained in the $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers.

Received 21st September 2018
Accepted 20th November 2018

DOI: 10.1039/c8ra07863g

rsc.li/rsc-advances

1 Introduction

Shale gas is an important natural gas resource, and distributed in many countries, such as China, Argentina, Algeria, U.S., Canada, Mexico, Australia, South Africa, and Russia *etc.*¹ For U.S. dry natural gas production, shale gas as the largest contributor has rapidly grown by 40% from 9.7 trillion cubic feet in 2012 to 13.6 trillion cubic feet in 2015.^{2,3} Natural gas is one of the primary fuels composed of approximately 90% of methane, which is widely used as a fuel and chemical feedstock for the conversion of methane to generate a number of products, for instance, hydrogen, liquid fuels, chemicals, heat, and electricity.⁴ However, carbon dioxide (CO_2) is also generated during a variety of methane conversion processes. CO_2 is a major contributor to global warming and climate change. In order to combat global warming and mitigate the CO_2 emissions, various carbon capture, storage, and utilization technologies have recently been developed.

Chemical looping process (CLP) is considered to be a novel alternative for fuel combustion to achieve efficient energy generation as well as inherent CO_2 separation. A chemical looping system is typically comprised of a fuel reactor and an air reactor. Carbonaceous fuels are oxidized by metal oxides (oxygen carriers) in the fuel reactor to generate CO_2 and H_2O . The reduced oxygen carrier is subsequently oxidized and regenerated by air in the air reactor.

The performance of the oxygen carrier is crucial for CLP development and is greatly influenced by the characteristics of

metal oxide and support material. Fe-based oxygen carriers are frequently applied for chemical looping combustion of gaseous fuel; however, sintering and attrition during continuous and high-temperature operations would decrease the reactivity of these oxygen carriers. Therefore, oxygen carriers of mixed metal oxide and support material are frequently employed for chemical looping operations to retard the sintering of oxygen carriers and to enhance their mechanical strength.⁵ Adánez *et al.*⁶ studied the CLC of methane in a thermogravimetric analyzer (TGA) using hematite as active phase and supported by various inert materials, and also reported that $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{ZrO}_2$ oxygen carriers containing 40–80 wt% Fe_2O_3 sintered at above 1100 °C exhibited high reactivity with methane and delivered high crush strength. Johansson *et al.*⁷ utilized the Fe_2O_3 supported with MgAl_2O_4 as an oxygen carrier to investigate their reactivity properties on the CLC of methane in a fluidized bed reactor. The results indicated that 60 wt% $\text{Fe}_2\text{O}_3/\text{MgAl}_2\text{O}_4$ oxygen carriers sintered at 1100 °C demonstrated high reactivity regarding methane combustion. In addition, the crush strength of $\text{Fe}_2\text{O}_3/\text{MgAl}_2\text{O}_4$ particles ranged of 125 to 180 μm was determined to be about 1.8 N. Zafar *et al.*⁸ investigated Fe_2O_3 on the MgAl_2O_4 and SiO_2 supports in a fluidized bed reactor for CLC application, and found that the $\text{Fe}_2\text{O}_3/\text{MgAl}_2\text{O}_4$ oxygen carriers showed high reactivity with methane during the Fe_2O_3 reduced to Fe_3O_4 , whereas the poor reactivity with methane was observed during the Fe_3O_4 reduced to FeO . Besides, the unreactive iron silicate was formed at high temperature by using SiO_2 as support. Corbella and Palacios⁹ revealed the methane conversion was reached about 90% for methane combustion with titania supported Fe_2O_3 oxygen carriers in a fixed bed reactor operated at 900 °C, and also

Department of Chemical Engineering, National Taiwan University of Science and Technology, Taipei 10607, Taiwan. E-mail: ku508@mail.ntust.edu.tw



reported that the low oxygen capacity was caused in the reduction stage because the interaction between iron-containing active phase and the support material lead to the formation of an irreducible phase FeTiO_3 . Li *et al.*¹⁰ indicated TiO_2 as support can markedly lower the energy barrier for O^{2-} migration within the dense solid phase, thus enhancing the O^{2-} diffusivity.¹⁰ Qin *et al.*¹¹ stated the vacancy defect is easy to form on the FeTiO_3 surface because the vacancy formation energy of FeTiO_3 is lower than Fe_2O_3 in the reduction stage. Consequently, the enhancing the porous surface structure formation on FeTiO_3 . However, Zhao and Shadman¹² observed that phase separation of iron oxide phase and titania phase during the redox cycles. Iron oxide migrates to the surface of FeTiO_3 during the oxidation, which could fracture the ilmenite particle. This mechanism might lower the particle strength.

In this study, alumina is selected as support to improve the mechanical strength of iron-based oxygen carrier, and titania is employed as another support to promote the reactivity. Based on our previous research results, the components of the $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers were optimized to achieve the better reactivity during TGA tests and mechanical strength.^{13,14} The optimized composition of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers were determined to be 60/40 and 70/20/10 in weight percentage. Alumina and alumina/titania supported Fe_2O_3 oxygen carriers ($\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$) were fabricated to investigate their reactivity properties in a fixed bed reactor. The effect of operating temperature and inlet gas concentration on the combustion of CH_4 with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers in a fixed bed reactor was examined and analyzed by shrinking core model (SCM). Preliminarily kinetic study for CLC of methane with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers are performed based on the experimental results from this study. Furthermore, the performance of the moving bed reactor using iron-based oxygen carriers was also discussed in this study. $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers were employed for chemical looping combustion of methane in a moving bed reactor (MBR) operated with the various $\text{CH}_4/\text{Fe}_2\text{O}_3$ ratio. The methane conversion, carbon conversion, and oxygen carrier conversion for methane combustion by $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers were evaluated by the moving bed reactor. The crystalline phases of the reduced oxygen carrier after the moving bed operation were identified by X-ray diffraction (XRD). Heat analysis for chemical looping combustion of methane was employed to evaluate the heat balance of input and output processing capacities.

2 Experimental

2.1 Preparation of various iron-based oxygen carriers

$\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ particles were prepared to serve as oxygen carriers in this study. $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carriers were formulated with 60 wt% hematite (99.9% Fe_2O_3 , China Steel) and 40 wt% alumina (99% Al_2O_3 , Chin Jung). $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ were formulated with 70 wt% hematite, 20 wt% alumina and 10 wt% titania. Hematite, alumina and titania particles of roughly 1 μm were mixed in deionized water

and dried at 80 $^\circ\text{C}$ for 6 hours to form a cake, and were then pulverized and screened for sizes between 1.2 and 1.4 mm. The $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ particles were later sintered at 1300 $^\circ\text{C}$ and 1200 $^\circ\text{C}$ for 2 hours in a muffle furnace, respectively. The crush strength of prepared oxygen carriers was analyzed by a texture machine (TA.XT plus), and the attrition of prepared oxygen carriers was examined by an attrition analyzer following ASTM methods D4058-96. The true density, particle density and bulk density of prepared oxygen carriers were determined by eqn (1) and (2), respectively, similar defines and results were reported by previous researchers.¹⁵

$$\rho_p = (1 - \phi)\rho_t \quad (1)$$

$$\rho_b = (1 - \varepsilon)\rho_p \quad (2)$$

where ρ_t is the true density of the oxygen carrier without the pores which presented in the oxygen carrier; ρ_p is the particle density of the oxygen carrier including the pores, which was measured by the Archimedes method; is the bulk density of the oxygen carrier; ϕ is 49.13% and 59.60% as the porosity of prepared $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$, respectively; ε is the fraction of void contained in the packed $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers, which were determined to be 41.61% and 40.17%, respectively. The main physicochemical properties of these prepared iron-based oxygen carriers are shown in Table 1.

A porosity of fresh oxygen carriers was measured by Archimedes method in water. The porosities of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers were determined to be 49.13% and 59.60%, respectively. The physical properties of 60 wt% $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carriers reported by De Vos *et al.*¹⁶ were similar to the results of this study that the porosity was obtained to be in the range of 49.10–59.70%.¹⁶ From the literature published by Breault *et al.*¹⁷ illustrated that the disappear of small grains due to the growth of larger grain promoted by high-temperature calcination, hence, the grain size and porosity become larger, while the specific surface area becomes smaller.¹⁷ Breault *et al.*¹⁷ also reported that as the calcination temperature is raised to 1000 $^\circ\text{C}$, the specific surface area of hematite particles was dropped from 6.0 to 0.3 $\text{m}^2 \text{g}^{-1}$.¹⁷ A similar result was observed in this study, the specific surface area of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers

Table 1 Main physicochemical properties of the iron-based oxygen carriers

Parameters	Unit	$\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$	$\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$
Fe_2O_3 fraction	wt%	60	70
Particle size	mm	1.2–1.4	1.2–1.4
True density, ρ_t	kg m^{-3}	4673	4795
Particle density, ρ_p	kg m^{-3}	2377	1937
Bulk density, ρ_b	kg m^{-3}	1388	1159
Porosity	%	49.13	59.60
Fraction void	%	41.61	40.17
Crushing strength	N	30.53	10.25
Attrition	%	4.01	16.83
Specific surface area, BET	$\text{m}^2 \text{g}^{-1}$	0.61	0.64



determined by BET analysis were 0.61 and 0.64 m² g⁻¹ at calcination temperatures of 1300 °C and 1100 °C, respectively.

2.2 Establishment of the fixed bed reactor system

A fixed-bed reactor system composed of a 25.4 mm ID SS310 reactor and with a PID-controlled heating element covering 200 mm of reactor length employed in this study is shown in Fig. 1. A plate with sixteen 0.25 mm apertures was located in the lower part of the reactor for supporting 40 g of prepared Fe₂O₃/Al₂O₃ particles or 30.2 g of prepared Fe₂O₃/Al₂O₃/TiO₂ particles. The temperature of the loaded reactor was then increased from room temperature with a ramping rate of 10 °C min⁻¹ and eventually kept at a specific operating temperature, ranging from 875 to 925 °C. For reduction experiments, methane was introduced into the reactor at a flow rate of 1 L min⁻¹ at different concentrations, ranging from 5 to 20%. After reduction, N₂ was introduced for sweeping reducing gas contained in the reactor. Air at a flow rate of 1 L min⁻¹ was subsequently introduced for 30 minutes to oxidize the reduced oxygen carriers. The outlet stream from the reactor was passed through a cold trap to condense steam, and was consequently analyzed by a non-dispersive infrared sensor (NDIR, Molecular Analysis 6000i) and a gas chromatography equipped with a thermal conductivity detector (GC-TCD, China Chromatography 2000) to detect the concentrations of carbon dioxide, carbon monoxide, methane, hydrogen, and oxygen.

2.3 Establishment of the moving bed reactor system

Schematic diagram of the annular dual-tube moving bed reactor (ADMBR) employed in this study is shown in Fig. 2. The reactor was composed of a 76.20 mm ID SS310S outer tube covered with an electric heating element to provide isothermally atmosphere, and a 25.40 mm ID SS310S inner tube. Roughly 3.0 kg of prepared Fe₂O₃/Al₂O₃ oxygen carriers or 2.5 kg of prepared Fe₂O₃/Al₂O₃/TiO₂ oxygen carriers were initially packed in the spacing between inner and outer tubes of the ADMBR. Fe₂O₃/Al₂O₃ and Fe₂O₃/Al₂O₃/TiO₂ oxygen carriers were then continuously fed into the packed reactor by a screw conveyor at flow rate operated at 29.53 and 20.72 g min⁻¹, respectively. Methane was fed into inner tube to serve as gaseous fuel, and N₂ was also introduced into the inner tube at a flow rate of 2.2 L min⁻¹. The fuel gas was then passing through the bottom of the inner tube

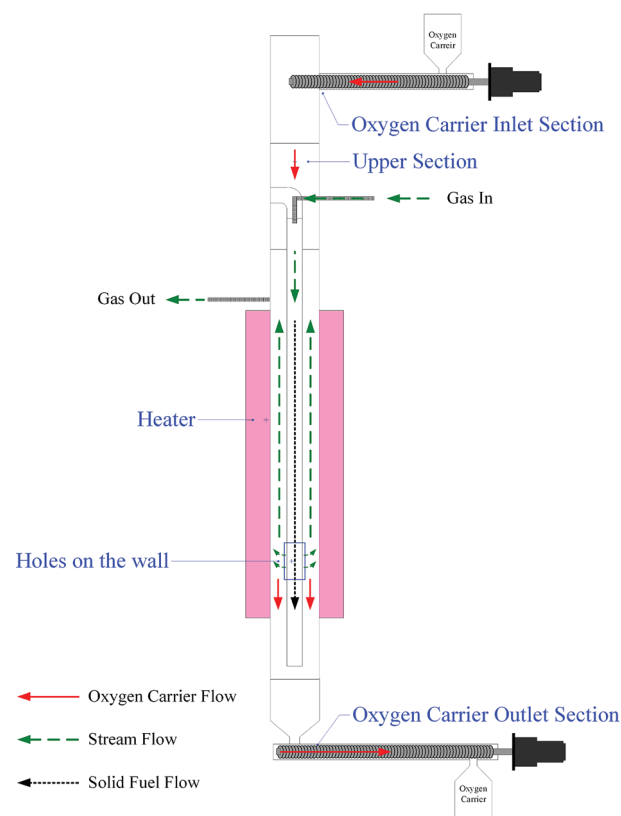


Fig. 2 Schematic diagram of the moving bed reactor system used in this study for methane combustion.

for consequent combustion with Fe-based oxygen carriers fed into and moved through the moving bed reactor. The reduced oxygen carriers were collectively removed out of the fuel reactor by another screw conveyor. The outlet stream from the moving bed reactor was cooled by a cold trap to condense water vapour and was afterward analyzed by a gas chromatography equipped with a thermal conductivity detector (GC-TCD, China Chromatography 2000) to detect the concentration of H₂ and a non-dispersive infrared sensor (NDIR, Molecular Analysis 6000i) to detect the concentration of CO₂, CO, CH₄, and O₂. The phase transformation of prepared oxygen carriers during methane combustion was characterized by X-ray diffraction (XRD).

3 Results and discussion

3.1 Methane combustion with iron-based oxygen carriers in a fixed bed reactor

Moving bed reactor (MBR) with counter-flow for solids and gases were proposed to enhance the utilization of available oxygen in the oxygen carriers.¹⁸ In order to estimate the influence of thermal and chemical effects only on the oxygen carrier reduction, a fixed bed reactor was used instead of moving beds. Indeed, the fixed bed allows avoiding any flow of the material, and the performance of the oxygen carrier in this kind of reactor may only be the consequence of chemical and thermal effects. The reactivity of prepared Fe₂O₃/Al₂O₃ and Fe₂O₃/Al₂O₃/TiO₂ oxygen carriers were investigated and conducted in the fixed


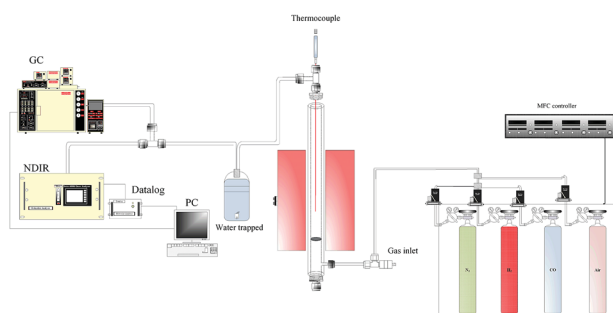


Fig. 1 Schematic diagram of the fixed bed reactor system used in this study for CLP operation.



bed reactor operated at the temperature between 875 and 925 °C by feeding CH₄/N₂ gas mixtures containing 5 to 20 vol% CH₄. The iron-based oxygen carriers are fully reduced for methane combustion as described by reaction (3).^{4,19,20}



Based on the mass balances of oxygen and hydrogen, the reduction conversion of iron-based oxygen carriers for methane combustion is determined as:

$$X_{\text{red}} = \frac{\int (2F_{\text{CO}_2} + F_{\text{CO}} + F_{\text{H}_2\text{O}}) dt}{\left(\frac{x_{\text{Fe}_2\text{O}_3} \cdot m_{\text{OC}}}{M_{\text{Fe}_2\text{O}_3}} \right)} \quad (4)$$

$$F_{\text{H}_2\text{O}} = 2F_{\text{CH}_4, \text{in}} - (2F_{\text{CH}_4} + F_{\text{H}_2}) \quad (5)$$

where $F_{\text{CH}_4, \text{in}}$ is the inlet mole flow rate (mmol min⁻¹) of CH₄; F_i is the outlet molar flow rate (mmol min⁻¹) of species i , i is denoted as CO₂, CO, H₂O, H₂, and CH₄; m_{OC} is the weight (g) of oxygen carriers packed in the reactor; $x_{\text{Fe}_2\text{O}_3}$ is the fraction of Fe₂O₃ contained in the oxygen carriers; $M_{\text{Fe}_2\text{O}_3}$ is 159.69 g mol⁻¹ as the molecular weight of Fe₂O₃. Fig. 3 shows the effect of operating temperature on the reduction of iron-based oxygen carriers with methane. The reduction conversions of Fe₂O₃/Al₂O₃/TiO₂ oxygen carriers calculated for experiments conducted with constant operation time are significantly higher than that of Fe₂O₃/Al₂O₃ oxygen carriers and are increased with higher operating temperatures. For instance, more than 95% Fe₂O₃/Al₂O₃/TiO₂ is reduced by methane at about 84 minutes for experiments conducted at 925 °C, much higher than that for Fe₂O₃/Al₂O₃ reduction with methane. Fig. 4 demonstrates the effect of inlet methane concentrations on the CLC of CH₄ by iron-based oxygen carriers. The conversions of Fe₂O₃/Al₂O₃ and Fe₂O₃/Al₂O₃/TiO₂ reduction are increased for experiments conducted with greater inlet methane concentrations, possibly because of the existence of more methane molecules. More methane molecules are more ready to react with Fe₂O₃

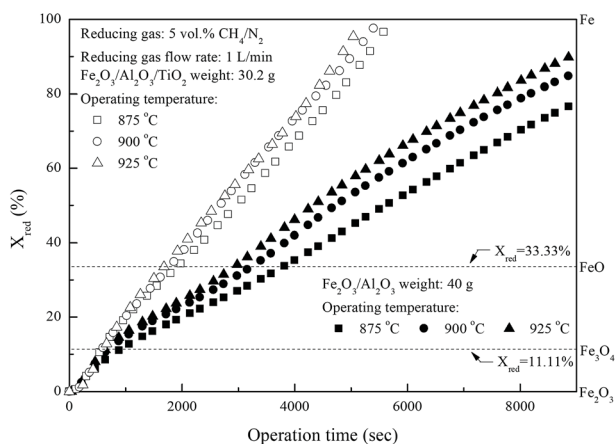


Fig. 3 Effect of operating temperature on the reduction of Fe₂O₃/Al₂O₃ and Fe₂O₃/Al₂O₃/TiO₂ with CH₄ in the fixed bed.

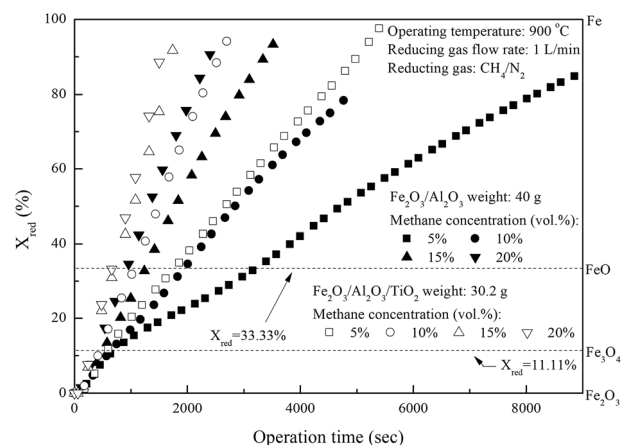


Fig. 4 Effect of inlet CH₄ concentrations on the reduction of Fe₂O₃/Al₂O₃ and Fe₂O₃/Al₂O₃/TiO₂ with CH₄ in the fixed bed.

contained in the iron-based oxygen carriers to generate CO₂ and H₂O, as described by reaction (3).

In this study, the temporal behaviour of iron-based oxygen carrier reduction for methane combustion is described by a shrinking core model (SCM), as exercised by most researchers for the application of various oxygen carriers for chemical looping:^{21–23}

$$1 - X_{\text{red}} = \left(\frac{r}{R} \right)^3 \quad (6)$$

$$t = \tau_{\text{gf}} X_{\text{red}} + \tau_{\text{pl}} \left[1 - 3(1 - X_{\text{red}})^{\frac{2}{3}} + 2(1 - X_{\text{red}}) \right] \quad (7)$$

$$\tau_{\text{gf}} = \frac{1000 x_{\text{Fe}_2\text{O}_3} \rho_{\text{p}} R}{3b C_{\text{Ag}} M_{\text{Fe}_2\text{O}_3} k_{\text{g}}} \quad (8)$$

$$\tau_{\text{pl}} = \frac{1000 x_{\text{Fe}_2\text{O}_3} \rho_{\text{p}} R^2}{6b C_{\text{Ag}} M_{\text{Fe}_2\text{O}_3} D_{\text{e}}} \quad (9)$$

$$D_{\text{e}} = D_{\text{pl},0} e^{-\frac{E_{\text{apl}}}{R_{\text{g}} T} - k_{\text{d}} X_{\text{red}}} \quad (10)$$

$$k_{\text{d}} = k_{\text{d},0} e^{-\frac{E_{\text{ad}}}{R_{\text{g}} T}} \quad (11)$$

where R and r are the radius (m) of the fresh particle and the unreacted core; τ_{gf} and τ_{pl} are the time (s) required for complete conversion of the oxygen carrier when the reaction is controlled by the gas-film diffusion and the product layer diffusion; C_{Ag} is the inlet molar concentration (mol m⁻³) of the gaseous fuel; b is the stoichiometric coefficient of gaseous fuel combusted with Fe₂O₃, which is determined to be 4/3 by reaction (3); k_{g} is the mass transfer coefficient (m s⁻¹) between gaseous fuel and oxygen carriers; D_{e} is the effective diffusion coefficient (m² s⁻¹) of gaseous fuel in the product layer; $D_{\text{pl},0}$ (m² s⁻¹) and E_{apl} (kJ mol⁻¹) are the pre-exponential factor and activation energy for the product layer diffusion reaction; k_{d} , $k_{\text{d},0}$ and E_{ad} (kJ mol⁻¹) are the decay constant, pre-exponential factor and activation energy for the product layer diffusivity; R_{g} is the ideal gas constant; T (K) is the operation temperature.



The reduction kinetics of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ with methane are regressed and calculated by the shrinking core model (SCM), as described in eqn (6)–(11). After fitting the conversion curves, the kinetic parameters are summarized in Table 2. As listed in Table 2, the mass transfer coefficient (k_g) of around 0.07 mm s^{-1} is calculated for the reduction of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ with methane, while the k_g of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ for methane combustion reached 0.12 mm s^{-1} , indicating that the reaction rate of methane for $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ reduction is faster than that for $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ reduction. Less $D_{\text{pl},0}$ is obtained for experiments with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carriers than those with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers, explicitly, demonstrating that the methane more easily diffusion through the product layer of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers. Moreover, the influence of operating temperature on the oxygen carrier conversions for the reduction of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ with methane are more than that for $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ reduction with methane, as shown in Fig. 3, because high activation energy for the product layer diffusion reaction (E_{apl}) is obtained for $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ reduction with methane. Furthermore, the slope of the reduction conversion vs. time curves is observed to be altered for experiments conducted at the various operating temperature, which may be also attributed to the decay constant (k_d) is dependent on the operating temperatures, similar to the results reported by previous researchers.^{23,24} For experiments conducted with operating temperature of 900°C , the slope of the reduction conversion vs. time curves for $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ reduction is significantly changed with inlet methane concentration ranged from 5 to 20%, as shown in Fig. 4, possibly due to high $k_{\text{d},0}$ is obtained for $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ reduction with CH_4 .²²

In this study, the gas-film diffusion and the product layer diffusion were major reaction resistances contributed for $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ reduction with methane in the fixed bed reactor. Cabello *et al.*²² studied that the kinetic study of 20 wt% $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carrier for gaseous fuel combustion by chemical looping process, and also indicated that the reduction reactions are controlled by the chemical reaction in the grain surface and the diffusion through the product layer of FeAl_2O_4 around the grains. This can be attributed to the external diffusion resistance is eliminated by using a small mass of solid sample (50 mg).²² Comparing the results from the literature and this study, methane more easily diffusion through the product layer of 20 wt% $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carriers, while less temperature effect on the reduction conversion was observed for experiments with both iron-based oxygen carriers. The reason is due to the $D_{\text{pl},0}$ and E_{pl} obtained here were significantly lower than that found in the literature.²² Additionally, the

intensity of the reaction rate for reduction of both iron-based oxygen carriers with methane was significantly changed with various methane concentration probably due to higher $k_{\text{d},0}$ and higher E_d were obtained in this work.

3.2 Methane combustion with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carriers in the ADMBR

Chemical looping combustion of methane was conducted in the ADMBR at 900°C by feeding $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carriers at flow rate of 29.53 g min^{-1} and CH_4 at flow rate from 328.4 to $985.3 \text{ mg min}^{-1}$. The main components of outlet streams for the combustion of methane from the moving bed reactor operated at different inlet CH_4 flow rates were determined to be CO_2 , CH_4 , H_2 and slightly CO in this study, as illustrated in Fig. 5. Outlet gas stream containing about 96% CO_2 and 4% CH_4 are achieved for experiments conducted with $\text{CH}_4/\text{Fe}_2\text{O}_3$ ratio ranged from 18.5 to 37.1 mg g^{-1} . However, CO_2 concentration of the outlet gas stream is rapidly reduced for experiments carried out with the $\text{CH}_4/\text{Fe}_2\text{O}_3$ ratio more than 37.1 mg g^{-1} . More CO and H_2 are observed due to the occurrence of incomplete methane combustion and methane decomposition reaction, as depicted by reaction (12).^{19,20} Based on carbon and hydrogen balance calculation, the steam generation rate ($F_{\text{H}_2\text{O}}$) and carbon deposition rate (F_{C}) for methane combustion are determined by eqn (5) and (13) and were also shown in Fig. 5.



$$F_{\text{C}} = F_{\text{CH}_4, \text{in}} - (F_{\text{CH}_4} + F_{\text{CO}_2} + F_{\text{CO}}) \quad (13)$$

The carbon deposition rate and steam generation rate of methane combustion by $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ in the ADMBR are found to be increased for experiments conducted with greater $\text{CH}_4/\text{Fe}_2\text{O}_3$ ratio. The increased in carbon deposition for experiments carried out at high $\text{CH}_4/\text{Fe}_2\text{O}_3$ ratio may be ascribed to the presence of excessive methane, thus more methane molecules are decomposed to generate carbon and hydrogen. CO_2 concentrations for CH_4 combustion conducted with $\text{CH}_4/\text{Fe}_2\text{O}_3$

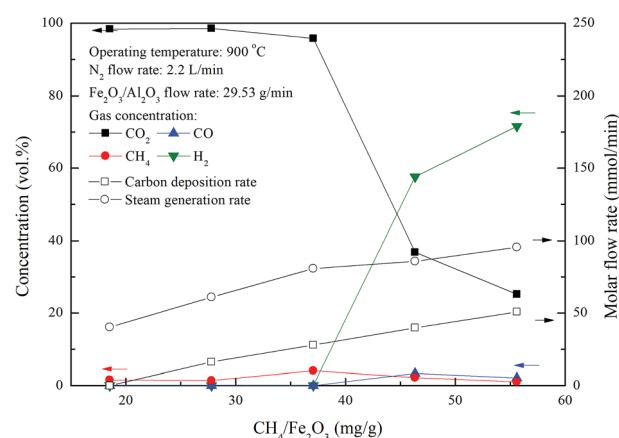


Fig. 5 Effect of methane flow rates on the combustion of methane with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ in the moving bed.

Table 2 Kinetics parameters for the reduction of iron-based oxygen carriers conducted with methane

Parameter	Unit	$\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$	$\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$
k_g	mm s^{-1}	0.07	0.12
$D_{\text{pl},0}$	$\text{mm}^2 \text{ s}^{-1}$	4.37×10^{20}	1.03×10^{21}
E_{apl}	kJ mol^{-1}	476.45	446.61
$k_{\text{d},0}$	—	3.08×10^{32}	7.88×10^{13}
E_{ad}	kJ mol^{-1}	736.19	305.41



ratio of 27.8 and 37.1 mg g⁻¹ were determined to be about 98% and 96%, respectively, indicating that hydrogen generated by methane decomposition was completely combusted by Fe₂O₃/Al₂O₃. Moreover, hydrogen was detected in the outlet stream for experiments operated at CH₄/Fe₂O₃ ratio more than 37.1 mg g⁻¹, possibly due to more hydrogen generated by methane decomposition was higher than that consumed by Fe₂O₃/Al₂O₃ reduction reaction.

The carbonaceous gases (CO₂, CO and CH₄) and deposited carbon are generated by methane combustion and decomposition. Therefore, carbon conversion (X_C) is the conversion of inlet methane to carbonaceous gases in the fuel reactor, as described as eqn (14). Based on the oxygen balance, the methane conversion (X_{methane}) and oxygen carrier conversion (X_{OC}) for CH₄ combustion were determined by eqn (15) and (16).^{25,26}

$$X_C = \frac{F_{\text{CO}_2} + F_{\text{CO}} + F_{\text{H}_2\text{O}}}{F_{\text{CH}_4, \text{in}}} \quad (14)$$

$$X_{\text{methane}} = \frac{2F_{\text{CO}_2} + F_{\text{CO}} + F_{\text{H}_2\text{O}}}{4F_{\text{CH}_4, \text{in}}} \quad (15)$$

$$X_{\text{OC}} = \frac{2F_{\text{CO}_2} + F_{\text{CO}} + F_{\text{H}_2\text{O}}}{\left(\frac{X_{\text{Fe}_2\text{O}_3} \dot{m}_{\text{OC}}}{M_{\text{Fe}_2\text{O}_3}}\right) \times 1000 \times 3} \quad (16)$$

where \dot{m}_{OC} is the mass flow rate (g min⁻¹) of the oxygen carriers in the ADMBR. As illustrated in Fig. 6, X_C and X_{methane} are significantly decreased for experiments carried out with increasing CH₄/Fe₂O₃ ratio for the combustion of methane with Fe₂O₃/Al₂O₃ oxygen carriers in the ADMBR operated at 900 °C, indicating excessive methane is provided. Experimental results obtained in this study suggest that the complete combustion reaction between CH₄ and Fe₂O₃/Al₂O₃ oxygen carriers could be accomplished for experiment conducted with CH₄/Fe₂O₃ ratio of 18.5 mg g⁻¹. As also indicated in Fig. 6, nearly 24.2% of the oxygen carrier conversion is achieved for the complete

combustion of methane with Fe₂O₃/Al₂O₃ oxygen carriers, demonstrating the Fe₂O₃/Al₂O₃ oxygen carriers operated in a moving bed reactor is majorly reduced to Fe₃O₄ and FeO, similar to the results reported by previous study.²⁷ However, oxygen carrier conversion for CLC of methane is found to be slightly enhanced for experiments conducted with greater CH₄/Fe₂O₃ ratio, because more Fe₂O₃/Al₂O₃ oxygen carriers are considered to be reduced by fuel gases, such as CH₄, CO and H₂, which is generated by methane combustion and decomposition.

3.3 Methane combustion with Fe₂O₃/Al₂O₃/TiO₂ oxygen carriers in the ADMBR

Chemical looping combustion of methane by Fe₂O₃/Al₂O₃/TiO₂ oxygen carriers for experiments conducted with various CH₄/Fe₂O₃ ratio were examined in this study. The outlet gas streams for combustion experiments of methane were composed mainly of CO₂, CH₄, H₂ and CO, as illustrated in Fig. 7. Outlet gas stream of nearly 100% CO₂ is achieved for experiments conducted with CH₄/Fe₂O₃ ratio of 22.6 mg g⁻¹. However, CO₂ concentration of the outlet gas stream for CLC of methane are found to be decreased for experiments carried out with CH₄/Fe₂O₃ ratio more than 34.0 mg g⁻¹, whereas H₂ and CO concentrations are increased. Besides, methane concentration of the outlet gas stream for methane combustion with Fe₂O₃/Al₂O₃/TiO₂ is enhanced for experiments conducted with CH₄/Fe₂O₃ ratio ranged from 34.0 to 45.3 mg g⁻¹. Subsequently, CH₄ concentration of the outlet gas stream is reduced for experiments conducted with CH₄/Fe₂O₃ ratio above 45.3 mg g⁻¹, possibly due to the occurrence of methane reforming reaction, as depicted by reaction (17).^{28,29} Thus, less steam generation rate is observed for the combustion of methane with Fe₂O₃/Al₂O₃/TiO₂ than that for methane combustion with Fe₂O₃/Al₂O₃, as illustrated in Fig. 7.

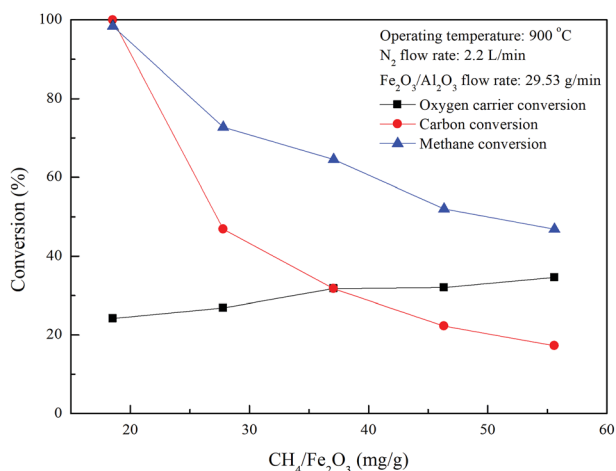



Fig. 6 Effect of methane flow rates on fuel and oxygen carrier conversions for CLC of methane with Fe₂O₃/Al₂O₃.

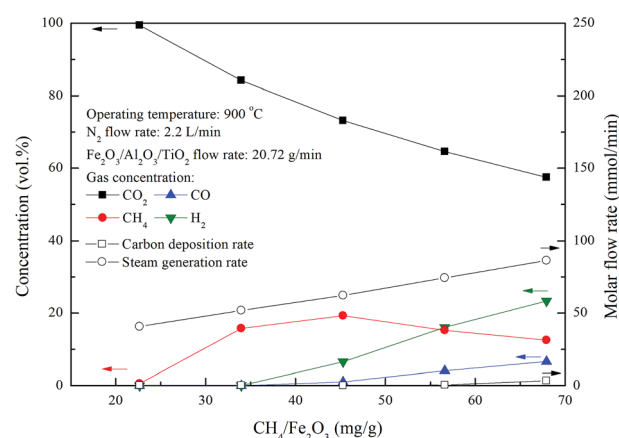


Fig. 7 Effect of methane flow rates on the combustion of methane with Fe₂O₃/Al₂O₃/TiO₂ in the moving bed.



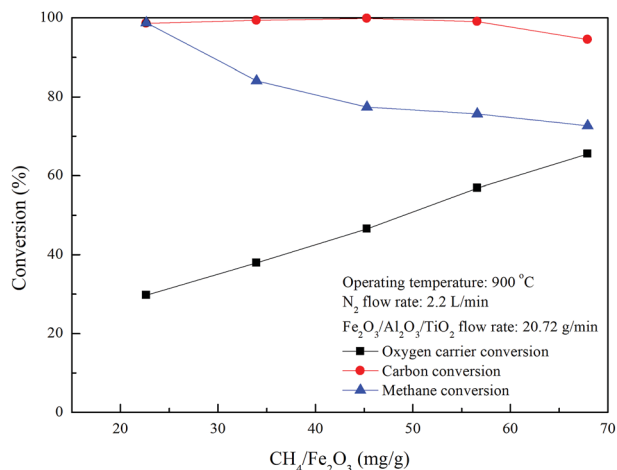


Fig. 8 Effect of methane flow rates on fuel and oxygen carrier conversions for CLC of methane with Fe₂O₃/Al₂O₃/TiO₂.

As shown in Fig. 5 and 7, the carbon deposition rate for methane combustion with Fe₂O₃/Al₂O₃/TiO₂ is noticeably lower than that for methane combustion with Fe₂O₃/Al₂O₃, indicating carbon deposition is significantly reduced as methane is combusted with Fe₂O₃/Al₂O₃/TiO₂ oxygen carriers. Carbon deposition is impeded because the reactivity of Fe₂O₃/Al₂O₃/TiO₂ oxygen carriers for methane combustion is higher than that of Fe₂O₃/Al₂O₃ oxygen carriers. Fig. 8 demonstrates that high carbon conversions (approximately 99%) are obtained for methane combustion conducted with CH₄/Fe₂O₃ ratio ranged from 22.6 to 56.6 mg g⁻¹, while the carbon conversion of methane combustion reached about 94.5% for experiments carried out with CH₄/Fe₂O₃ ratio of 67.9 mg g⁻¹, due to the insufficient oxygen carriers are provided to react with methane. Thus, methane molecules are slightly decomposed to generate carbon and hydrogen. As also illustrated in Fig. 8, methane is completely combusted by Fe₂O₃/Al₂O₃/TiO₂ oxygen carriers for experiment conducted with CH₄/Fe₂O₃ ratio of 22.6 mg g⁻¹. However, as for experiment conducted with CH₄/Fe₂O₃ ratio more than 22.6 mg g⁻¹, the methane conversions are found to be decreased with increased with increasing CH₄/Fe₂O₃ ratio. The decreased in methane conversion for experiments carried out at high CH₄/Fe₂O₃ ratio may be ascribed to the occurrence of incomplete methane combustion and methane reforming reaction, thus more combustible gases are observed.

Oxygen carrier conversion of around 29.7% is achieved for the complete combustion of methane with Fe₂O₃/Al₂O₃/TiO₂ oxygen carrier, while the oxygen carrier conversions are enhanced for experiment conducted with CH₄/Fe₂O₃ ratio above 22.6 mg g⁻¹, as shown in Fig. 8, further demonstrating increased CH₄/Fe₂O₃ ratio to promote the Fe₂O₃/Al₂O₃/TiO₂ reduction. Besides, Fe₂O₃/Al₂O₃ flowrate of around 29.53 g min⁻¹ was provided for complete methane combustion, while the Fe₂O₃/Al₂O₃/TiO₂ flow rate needed to about 20.72 g min⁻¹ for the complete combustion of methane. Less oxygen carrier is demanded for the complete combustion of methane with Fe₂O₃/Al₂O₃/TiO₂ than that for methane combustion with Fe₂O₃/Al₂O₃, possibly due to the methane is considered to be consumed more rapidly by Fe₂O₃/Al₂O₃/TiO₂ reduction reaction than by Fe₂O₃/Al₂O₃ reduction reaction. Moreover, less oxygen carriers are required may also be ascribed to the higher Fe₂O₃ contained in the Fe₂O₃/Al₂O₃/TiO₂ oxygen carrier. Abad *et al.*²¹ analyzed the design criteria for a CLC system and reported that the solid circulation rate was decreased with increasing the *et al.* oxide content for the combustion of fuel gases (H₂, CO and CH₄) with different metal oxides (CuO, NiO, and Fe₂O₃).

As listed in Table 3, the gas hourly space velocity (GHSV) of CH₄/N₂ mixture was increased with increasing inlet methane concentration. Higher GHSV means higher fuel/oxygen carrier ratios and shorter residence time. Therefore, the increase in the GHSV led to a decrease of methane and carbon conversion, whereas an increase of oxygen carrier conversion.

3.4 Performance evaluation and heat analysis for CH₄ combustion

In order to differentiate the theoretical and actual Fe₂O₃ amount for the combustion of one mole of methane, a Fe₂O₃/CH₄ molar ratio was determined for evaluating the demand of oxygen carrier. For moving bed operation, a five-stage RGibbs reactor model has been shown to accurately simulate the experimental results for syngas and natural gas conversion.^{30,31} The parameters for the ASPEN Plus® model have been proposed by Li *et al.*¹⁸ and Kathe *et al.*³² The maximum fuel and oxygen carrier conversions for chemical looping combustion of methane with Fe₂O₃ in the counter-current moving bed reducer operated at 900 °C and 1 atm could be obtained from ASPEN simulation under the thermodynamic equilibrium. Based on the stoichiometry calculation, 4/3 mole of Fe₂O₃ are consumed for 1 mole of methane combustion, indicating the minimum

Table 3 The operating conditions of methane combustion with iron-based oxygen carriers in the moving bed reactor^a

$F_{\text{CH}_4, \text{in}}$ mmol min ⁻¹	$C_{\text{CH}_4, \text{in}}$ vol%	GHSV h ⁻¹	Fe ₂ O ₃ /Al ₂ O ₃		Fe ₂ O ₃ /Al ₂ O ₃ /TiO ₂	
			\dot{m}_{OC} g min ⁻¹	CH ₄ /Fe ₂ O ₃ mg g ⁻¹	\dot{m}_{OC} g min ⁻¹	CH ₄ /Fe ₂ O ₃ mg g ⁻¹
20.5	18.52	295.1	29.53	18.54	20.72	22.64
30.7	25.42	322.4		27.80		33.96
41	31.25	349.8		37.07		45.29
51.2	36.23	377.1		46.34		56.61
61.4	40.54	404.4		55.61		67.93

^a GHSV: gas hourly space velocity; $F_{\text{CH}_4, \text{in}}$: the inlet mole flow rate of methane; $C_{\text{CH}_4, \text{in}}$: the inlet concentration of methane; \dot{m}_{OC} : the mass flow rate of the oxygen carriers in the ADMBR.



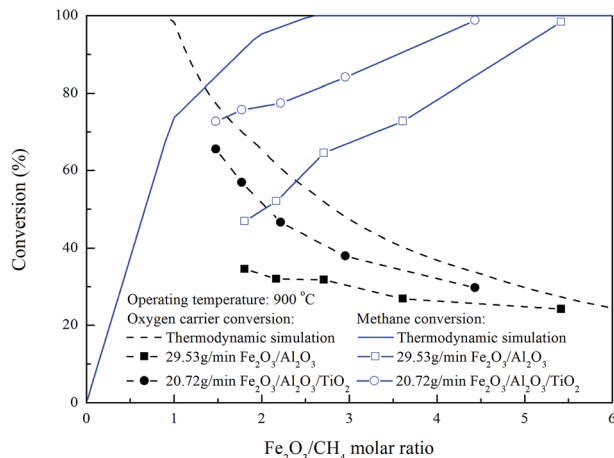


Fig. 9 Effect of $\text{Fe}_2\text{O}_3/\text{CH}_4$ molar ratio on fuel and oxygen carrier conversion for methane combustion in the moving bed.

Fe_2O_3 to CH_4 molar flow rate ratio is determined to be 1.33 for theoretically complete combustion of CH_4 . Experiments and ASPEN simulations to examine the effect of $\text{Fe}_2\text{O}_3/\text{CH}_4$ molar ratio on the fuel and oxygen carrier conversions were conducted with various $\text{Fe}_2\text{O}_3/\text{CH}_4$ molar ratio, and the results were shown in Fig. 9. The decrease in the oxygen carrier conversion is observed for ASPEN simulation carried out with $\text{Fe}_2\text{O}_3/\text{CH}_4$ molar ratio more than 0.9, while complete conversion of methane is achieved as $\text{Fe}_2\text{O}_3/\text{CH}_4$ molar ratio reached more than 2.6, similar to the results reported by previous study.^{25,32} For the complete methane combustion, higher $\text{Fe}_2\text{O}_3/\text{CH}_4$ molar ratio is determined by ASPEN simulation than that by stoichiometry calculation, which may be attributed to the thermodynamic resistance, hence, Fe_2O_3 is not fully reduced to Fe for the complete combustion of methane.

Compared with the simulation result, the methane conversion for the combustion of methane with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers are increased for experiments conducted with higher $\text{Fe}_2\text{O}_3/\text{CH}_4$ molar ratio, and reached 98.4 and 98.8% as $\text{Fe}_2\text{O}_3/\text{CH}_4$ molar ratio reached 5.4 and 4.4, as also shown in Fig. 9. More oxygen carriers are required for experiments conducted with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carriers than that with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers, probably because lattice oxygen present in the $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers are more readily to react with combustible gas. Thus, the oxygen carrier conversions for the combustion of methane with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers are higher than that for methane combustion with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carriers.

According to the XRD patterns illustrated in Fig. 10, the crystalline phases of freshly prepared $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carriers are mainly Fe_2O_3 and Al_2O_3 . The oxygen carriers moved through the ADMBR was also sampled, and characterized to be mostly Al_2FeO_4 , indicating that the amount of oxygen utilization from Fe_2O_3 to FeO. Similar observation was reported by previous researchers.^{20,33} It has been reported that the crystal phase of Fe_3C might be formation during ASPEN simulation of chemical looping combustion of methane.²⁵ The formations of Fe_3C and Fe were observed for experiment conducted with $\text{CH}_4/\text{Fe}_2\text{O}_3$ ratio of 55.6 mg g^{-1} and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ flow rate of 29.53 g min^{-1} .

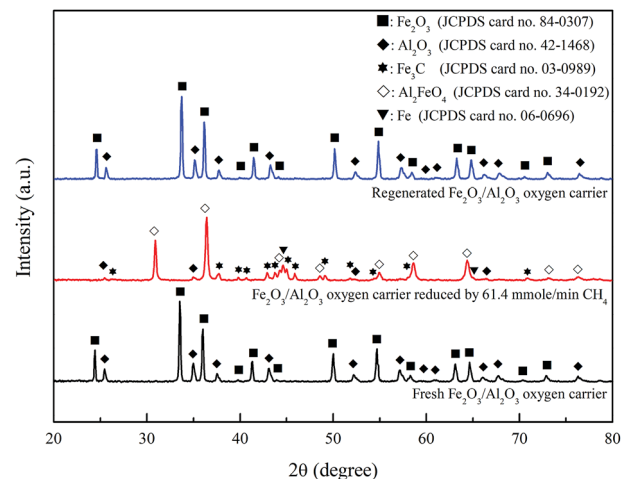


Fig. 10 X-ray diffraction patterns of fresh, reduced and regenerated $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carriers for methane combustion.

Takenaka *et al.*³⁴ analyzed the formation of filamentous carbon over supported Fe catalysts through methane decomposition, and also reported that Fe_3C formation is favored at the mass fraction of Fe_2O_3 contained in the $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ was more than 38%. Additionally, Fe_3C and Fe are the typical active species to be employed as catalyst for methane decomposition.^{34,35} Consequently, carbon deposition is also contributed by the Fe_3C and Fe generated by the reaction between methane and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carrier. Subsequently, the reduced $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carriers are completely oxidized by air in the air reactor to generate Fe_2O_3 and Al_2O_3 , which are observed in the XRD pattern.

The fresh $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ particles were characterized by XRD for phase identification as shown in Fig. 11. Fe_2O_3 , Fe_2TiO_5 and Al_2O_3 are the major crystalline phases of fresh oxygen carriers. For experiment conducted with $\text{CH}_4/\text{Fe}_2\text{O}_3$ ratio of 67.9 mg g^{-1} and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ flow rate of 20.72 g min^{-1} , the reduced $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers were sampled from moving bed operation. The absence of Fe_2O_3 , Fe_2TiO_5 and Al_2O_3 in the XRD pattern indicated that Fe_2O_3 and Fe_2TiO_5 is completely reduced. Hence, the crystalline phases of the reduced $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers are composed of Fe, Fe_3O_4 , Al_2FeO_4 and FeTiO_3 , as illustrated in Fig. 11. In addition, Al_2FeO_4 and FeTiO_3 generated during reduction might serve as support materials as well as oxygen carriers in practical operation by moving bed reactor for chemical looping process, similar to the results reported by previous study.^{13,36} For $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers sampled after regeneration, Fe_2O_3 , Fe_2TiO_5 and Al_2O_3 are observed in the XRD pattern, demonstrating that Fe, Fe_3O_4 , Al_2FeO_4 and FeTiO_3 contained in the reduced $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers were completely oxidized to Fe_2O_3 , Fe_2TiO_5 and Al_2O_3 .

The mechanism for reduction of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers with methane are proposed as reactions (18)–(24) based on the experimental results from this study. Unfortunately, from the analysis of the fixed bed curves, the reduction conversion contributed by each reduction reactions were not possible to be separated because these reduction




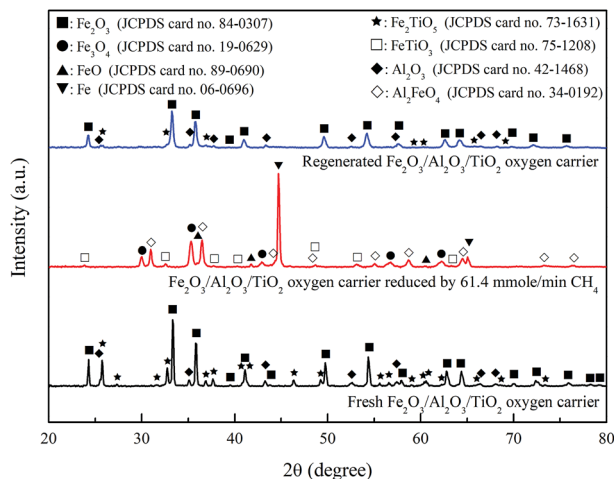






Fig. 11 X-ray diffraction patterns of fresh, reduced and regenerated $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers for methane combustion.

reactions may occur simultaneously. Therefore, as described by reaction (3), the overall reduction reaction of iron-based oxygen carrier for methane combustion is summarized and simplified by Integrated Rate of Reduction (IRoR) model, which has been widely used for evaluating the total reduction rate of iron ores.³⁷

For $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ reduction:



For $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ reduction:



The input processing capacity (Q_{in}) is the enthalpy of methane calculated as:

$$Q_{\text{in}} = \dot{m} \Delta H_{\text{Fuel}} \quad (25)$$

where \dot{m}_{OC} and ΔH_{Fuel} are the molar flow rate (mol s^{-1}) of methane and the higher heating value (kJ mol^{-1}), respectively. The heat balance analysis is determined by the following equation:

$$Q_{\text{in}} = Q_{\text{C,out}} + Q_{\text{unC,out}} \quad (26)$$

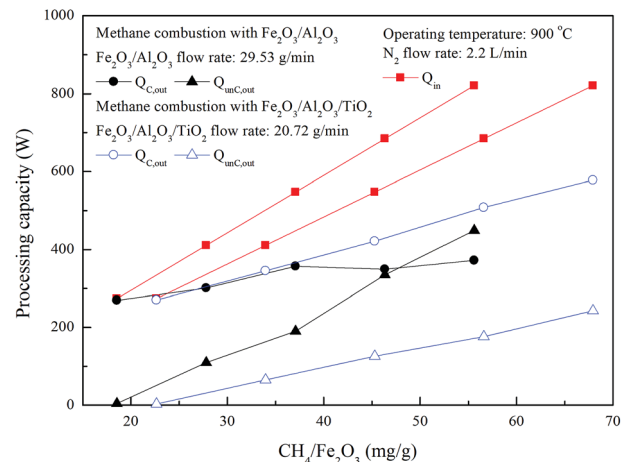


Fig. 12 Effect of methane flow rate on processing capacity for methane combustion in the moving bed.

where $Q_{\text{C,out}}$ and $Q_{\text{unC,out}}$ are the output processing capacity (W) for methane combustion and unburned, respectively. The output processing capacity for CLC and unburned is subsequently calculated by the following equations:

$$Q_{\text{C,out}} = \sum (F_{j,\text{in}} - F_{j,\text{out,C}}) \Delta H_{\text{rxn},j} \quad (27)$$

$$Q_{\text{unC,out}} = \sum F_{j,\text{out,C}} \Delta H_{\text{rxn},j} \quad (28)$$

where $F_{j,\text{in}}$ is the inlet mole flow rate of species j ; $F_{j,\text{out,C}}$ is the molar flow rate of species j generated by methane combustion; $\Delta H_{\text{rxn},j}$ is the enthalpy of species j ; j is denoted as CO, CH_4 , H_2 and C.

As shown in Fig. 12, 269 W and 270 W are released for methane combustion with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers in the ADMBR, indicating that roughly 98% of Q_{in} released for methane combustion using $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers in the ADMBR. Afterward, $Q_{\text{C,out}}$ for methane combustions with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers are increased for experiments conducted with higher $\text{CH}_4/\text{Fe}_2\text{O}_3$ ratio, and reached 578 W as methane conversion reached 72.7%. However, $Q_{\text{C,out}}$ for methane combustion with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carriers conducted with $\text{CH}_4/\text{Fe}_2\text{O}_3$ ratio greater than 37.1 mg g^{-1} , and reached 350 W as methane conversion reached less than 64.6%, as shown in Fig. 12. More heat is generated for combustion of methane by $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers, probably because methane is more fully to react with the Fe_2O_3 contained in the $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers. Moreover, less heat is generated for combustion of methane by $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carriers because more carbon deposition is formed.

4 Conclusions

Fe_2O_3 supported with Al_2O_3 and $\text{Al}_2\text{O}_3/\text{TiO}_2$ as oxygen carrier were investigated for CLC of methane. The reduction kinetic of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ with methane are agreeably described by a shrinking core model. The results indicated that the reduction rate of CH_4 for $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ reduction was



faster than that for $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ reduction, also indicated that the methane more easily diffusion through the product layer of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers. The activation energy for the product layer diffusion reaction ($E_{\text{a,pl}}$) estimated for CLP by employment of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ as oxygen carrier are about 476 and 447 kJ mol^{-1} for oxygen carrier reduction with methane, respectively. Approximately, methane is completely combusted for experiments conducted in the moving bed reactor with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ operated at $\text{Fe}_2\text{O}_3/\text{CH}_4$ molar ratio reached about 5.4 and 4.4, respectively; in addition, the oxygen carrier conversions are respectively reached about 24.2% and 29.7%. Carbon deposition during methane combustion is noticeably avoided by using $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ as oxygen carrier. According to the XRD characterization, Al_2FeO_4 is the major crystalline phase generated during CLC of methane with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ oxygen carrier. The formations of Fe_3C and Fe were observed for experiment conducted with $\text{CH}_4/\text{Fe}_2\text{O}_3$ ratio of 67.9 mg g^{-1} and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ flow rate of 29.53 g min^{-1} , which would serve as catalyst for methane decomposition. For $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers sampled after reduction, Fe , Fe_3O_4 , Al_2FeO_4 and FeTiO_3 were identified by the XRD pattern, demonstrating Al_2FeO_4 and FeTiO_3 generated during reduction might become support materials as well as oxygen carriers in practical operation by moving bed reactor for chemical looping process. Output processing capacity estimated for CLC by employment of $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ as oxygen carrier are increased for experiments conducted with higher $\text{CH}_4/\text{Fe}_2\text{O}_3$ ratio, and reached 350 W and 578 W as methane conversion reached around 64.6% and 72.7%, respectively. About 269 W and 270 W are released for complete methane combustion with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers in the ADMBR, indicating that roughly 98% of Q_{in} released for methane combustion using $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ and $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3/\text{TiO}_2$ oxygen carriers in the ADMBR.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This research was supported by Grant MOST 106-3113-E-007-002-from the National Science and Technology Program-Energy, Taiwan, and by Grant MOST 105-2622-E-011-019-CC2 and MOST 103-2221-E-011-002-MY3 from the Ministry of Science and Technology, Taiwan. The authors appreciated China Steel Corp. for providing hematite powders for the preparation of oxygen carriers.

References

- 1 World Energy Council (WEC), *World Energy Resources – Unconventional Gas, a Global Phenomenon*, 2016.
- 2 U.S. Energy Information Administration (EIA), *Annual Energy Outlook 2014 with Projections to 2040*, 2014.
- 3 U.S. Energy Information Administration (EIA), *Annual Energy Outlook 2016 with Projections to 2040*, 2016.
- 4 L. S. Fan, *Chemical Looping Systems for Fossil Energy Conversions*, John Wiley & Sons, Inc., New York, 2010.
- 5 J. Adánez, A. Abad, F. García-Labiano, P. Gayán and L. F. de Diego, Progress in Chemical-looping Combustion and Reforming Technologies, *Prog. Energy Combust. Sci.*, 2012, **38**, 215–282.
- 6 J. Adánez, L. F. de Diego, F. García-Labiano, P. Gayán, A. Abad and J. M. Palacios, Selection of Oxygen Carriers for Chemical-looping Combustion, *Energy Fuels*, 2004, **18**, 371–377.
- 7 M. Johansson, T. Mattisson and A. Lyngfelt, Investigation of Fe_2O_3 with MgAl_2O_4 for Chemical-looping Combustion, *Ind. Eng. Chem. Res.*, 2004, **43**, 6978–6987.
- 8 Q. Zafar, T. Mattisson and B. Gevert, Redox Investigation of Some Oxides of Transition-state Metals Ni, Cu, Fe, and Supported on SiO_2 and MgAl_2O_4 , *Energy Fuels*, 2006, **20**, 33–44.
- 9 B. M. Corbella and J. M. Palacios, Titania-supported Iron Oxide as Oxygen Carrier for Chemical-looping Combustion of Methane, *Fuel*, 2007, **86**, 113–122.
- 10 F. Li, S. Luo, Z. Sun, X. Bao and L. S. Fan, Role of Metal Oxide Support in Redox Reactions of Iron Oxide for Chemical Looping Applications: Experiments and Density Functional Theory Calculations, *Energy Environ. Sci.*, 2011, **4**, 3661–3667.
- 11 L. Qin, Z. Cheng, J. A. Fan, D. Kopechek, D. Xu, N. Deshpande and L. S. Fan, Nanostructure Formation Mechanism and Ion Diffusion in Iron-titanium Composite Materials with Chemical Looping Redox Reactions, *J. Mater. Chem. A*, 2015, **3**, 11302–11312.
- 12 Y. Zhao and F. Shadman, Kinetics and Mechanism of Ilmenite Reduction with Carbon Monoxide, *AIChE J*, 1990, **36**, 1433–1438.
- 13 P. C. Chiu, Y. Ku, Y. L. Wu, H. C. Wu, Y. L. Kuo and Y. H. Tseng, Characterization and Evaluation of Prepared $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ Oxygen Carriers for Chemical Looping Process, *Aerosol Air Qual. Res.*, 2014, **14**, 981–990.
- 14 M. C. Lo, *Composite Fe-Ti Based Oxygen Carrier for Chemical Looping Combustion and Hydrogen Generation*, Master Thesis in Department of Chemical Engineering, National Taiwan University of Science and Technology, Taipei City, Taiwan, 2014.
- 15 P. Markström and A. Lyngfelt, Designing and Operating a Cold-flow Model of a 100 kW Chemical-looping Combustor, *Powder Technol.*, 2012, **222**, 182–192.
- 16 Y. De Vos, M. Jacobs, P. Van Der Voort, I. Van Driessche, F. Snijders and A. Verberckmoes, Optimization of Spray Dried Attrition-resistant Iron Based Oxygen Carriers for Chemical Looping Reforming, *Chem. Eng. J.*, 2017, **309**, 824–839.
- 17 R. W. Breault, C. S. Yarrington and J. M. Weber, The Effect of Thermal Treatment of Hematite Ore for Chemical Looping Combustion of Methane, *J. Energy Resour. Technol.*, 2016, **138**, 0422021–0422028.
- 18 F. Li, L. Zeng, L. G. Velazquez-Vargas, Z. Yoscovits and L. S. Fan, Syngas Chemical Looping Gasification Process:



- Bench-scale Studies and Reactor Simulations, *AIChE J.*, 2010, **56**, 2186–2199.
- 19 P. Cho, T. Mattisson and A. Lyngfelt, Carbon Formation on Nickel and Iron Oxide-containing Oxygen Carriers for Chemical-looping Combustion, *Ind. Eng. Chem. Res.*, 2005, **44**, 668–676.
 - 20 Y. Ku, H. C. Wu, P. C. Chiu, Y. H. Tseng and Y. L. Kuo, Methane Combustion by Moving Bed Fuel Reactor with $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ Oxygen Carriers, *Appl. Energy*, 2014, **113**, 1909–1915.
 - 21 A. Abad, J. Adánez, F. García-Labiano, L. F. de Diego, P. Gayán and J. Celaya, Mapping of the Range of Operational Conditions for Cu-, Fe-, and Ni-based Oxygen Carriers in Chemical-looping Combustion, *Chem. Eng. Sci.*, 2007, **65**, 533–549.
 - 22 A. Cabello, A. Abad, F. García-Labiano, P. Gayán, L. F. de Diego and J. Adánez, Kinetic Determination of a Highly Reactive Impregnated $\text{Fe}_2\text{O}_3/\text{Al}_2\text{O}_3$ Oxygen Carrier for Use in Gas-fueled Chemical Looping Combustion, *Chem. Eng. J.*, 2014, **258**, 265–280.
 - 23 A. Abad, F. García-Labiano, P. Gayán, L. F. de Diego and J. Adánez, Redox Kinetics of $\text{CaMg}_{0.1}\text{Ti}_{0.125}\text{Mn}_{0.775}\text{O}_{2.9-\delta}$ for Chemical Looping Combustion (CLC) and Chemical Looping with Oxygen Uncoupling (CLOU), *Chem. Eng. J.*, 2015, **269**, 67–81.
 - 24 L. F. de Diego, A. Abad, A. Cabello, P. Gayán, F. García-Labiano and J. Adánez, Reduction and Oxidation Kinetics of a $\text{CaMn}_{0.9}\text{Mg}_{0.1}\text{O}_{3-\delta}$ Oxygen Carrier for Chemical-looping Combustion, *Ind. Eng. Chem. Res.*, 2014, **53**, 87–103.
 - 25 L. Zeng, A. Tong, M. Kathe, S. Bayham and L. S. Fan, Iron Oxide Looping for Natural Gas Conversion in a Countercurrent Moving Bed Reactor, *Appl. Energy*, 2015, **157**, 338–347.
 - 26 H. C. Wu and Y. Ku, Chemical Looping Gasification of Charcoal with Iron-based Oxygen Carriers in an Annular Dual-tube Moving Bed Reactor, *Aerosol Air Qual. Res.*, 2016, **16**, 1093–1103.
 - 27 S. Luo, S. Bayham, L. Zeng, O. McGivern, E. Chung, A. Majumder and L. S. Fan, Conversion of Metallurgical Coke and Coal Using a Coal Direct Chemical Looping (CDCL) Moving Bed Reactor, *Appl. Energy*, 2014, **118**, 300–308.
 - 28 P. C. Chiu and Y. Ku, Chemical Looping Process – a Novel Technology for Inherent CO_2 Capture, *Aerosol Air Qual. Res.*, 2012, **12**, 1421–1432.
 - 29 M. Kathe, C. Fryer, P. Sandvik, F. Kong, Y. Zhang, A. Empfield and L. S. Fan, Modularization Strategy for Syngas Generation in Chemical Looping Methane Reforming Systems with CO_2 as Feedstock, *AIChE J.*, 2017, **63**, 3343–3360.
 - 30 A. Tong, D. Sridhar, Z. Sun, H. R. Kim, L. Zeng, F. Wang, D. Wang, M. V. Kathe, S. Luo, Y. Sun and L. S. Fan, Continuous High Purity Hydrogen Generation from a Syngas Chemical Looping 25 kWth Sub-pilot Unit with 100% Carbon Capture, *Fuel*, 2013, **103**, 495–505.
 - 31 A. Tong, L. Zeng, M. V. Kathe, D. Sridhar and L. S. Fan, Application of the Moving-bed Chemical Looping Process for High Methane Conversion, *Energy Fuels*, 2013, **27**, 4119–4128.
 - 32 M. V. Kathe, A. Empfield, J. Na, E. Blair and L. S. Fan, Hydrogen Production from Natural Gas Using an Iron-based Chemical Looping Technology: Thermodynamic Simulations and Process System Analysis, *Appl. Energy*, 2016, **165**, 183–201.
 - 33 M. Ishida, K. Takeshita, K. Suzuki and T. Ohba, Application of $\text{Fe}_2\text{O}_3\text{--Al}_2\text{O}_3$ Composite Particles as Solid Looping Material of the Chemical-loop Combustor, *Energy Fuels*, 2005, **19**, 2514–2518.
 - 34 S. Takenaka, M. Serizawa and K. Otsuka, Formation of Filamentous Carbons Over Supported Fe Catalysts Through Methane Decomposition, *J. Catal.*, 2004, **222**, 520–531.
 - 35 C. Emmenegger, J. M. Bonard, P. Maun, P. Sudan, A. Lepora, B. Grobety, A. Züttel and L. Schlapbach, Synthesis of Carbon Nanotubes Over Fe Catalyst on Aluminum and Suggested Growth Mechanism, *Carbon*, 2003, **41**, 539–547.
 - 36 Y. Ku, Y. C. Liu, P. C. Chiu, Y. L. Kuo and Y. H. Tseng, Mechanism of Fe_2TiO_5 as Oxygen Carrier for Chemical Looping Process and Evaluation for Hydrogen Generation, *Ceram. Int.*, 2014, **40**, 4599–4605.
 - 37 A. Abad, J. Adánez, A. Cuadrat, F. García-Labiano, P. Gayán and L. F. de Diego, Kinetics of Redox Reactions of Ilmenite for Chemical-looping Combustion, *Chem. Eng. Sci.*, 2011, **66**, 689–702.

