

Cite this: *RSC Adv.*, 2019, 9, 28735

Ruthenium-decorated vanadium pentoxide for room temperature ammonia sensing

Shobha N. Birajdar,^a Neha Y. Hebalkar,^b Satish K. Pardeshi,^c Sulabha K. Kulkarni^{*a} and Parag V. Adhyapak^{id}^{*a}

Layer structured vanadium pentoxide (V_2O_5) microparticles were synthesized hydrothermally and successfully decorated by a facile wet chemical route, with ~ 10 – 20 nm sized ruthenium nanoparticles. Both V_2O_5 and ruthenium nanoparticle decorated V_2O_5 ($1\%Ru@V_2O_5$) were investigated for their suitability as resistive gas sensors. It was found that the $1\%Ru@V_2O_5$ sample showed very high selectivity and sensitivity towards ammonia vapors. The sensitivity measurements were carried out at $30^\circ C$ (room temperature), $50^\circ C$ and $100^\circ C$. The best results were obtained at room temperature for $1\%Ru@V_2O_5$. Remarkably as short a response time as 0.52 s @ 130 ppm and as low as 9.39 s @ 10 ppm recovery time at room temperature along with high selectivity towards many gases and vapors have been noted in the 10 to 130 ppm ammonia concentration range. Short response and recovery time, high reproducibility, selectivity and room temperature operation are the main attributes of the $1\%Ru@V_2O_5$ sensor. Higher sensitivity of $1\%Ru@V_2O_5$ compared to V_2O_5 has been explained and is due to dissociation of atmospheric water molecules on $1\%Ru@V_2O_5$ as compared to bare V_2O_5 which makes hydrogen atoms available on Brønsted sites for ammonia adsorption and sensing. The presence of ruthenium with a thin layer of oxide is clear from X-ray photoelectron spectroscopy and that of water molecules from Fourier transform infrared spectroscopy.

Received 11th June 2019
Accepted 31st August 2019

DOI: 10.1039/c9ra04382a

rsc.li/rsc-advances

1 Introduction

Vanadium oxides and their composites are of considerable research interest due to their selective catalytic and sensing activity, potential applications in electrochemical capacitors or supercapacitors, as well as potential for thermoelectric energy application.^{1–6} Catalytic and sensing activities mainly arise due to the interesting electronic structure of vanadium and its oxides. Vanadium has $3d^3 4s^2$ electrons in its outer shell, which enables it to be in various oxidation states viz. V^{2+} , V^{3+} , V^{4+} and V^{5+} . This makes it a complex as well as interesting material. Amongst the various vanadium oxides, vanadium pentoxide (V_2O_5) is widely used and is stable. It has been synthesized using various physico-chemical methods such as co-precipitation, vapor-solid method of thermal evaporation, hydrothermal, pulsed laser deposition *etc.*^{3,4,7,8} The literature also reports wire, belt, tube, needle, hollow nano-assemblies or flower like morphologies for V_2O_5 which depend upon the precursors used and synthesis procedures.^{8–17} However there is no report so far on small V_2O_5 particles catalyzed by ruthenium in detection of

ammonia at room temperature which is an important task. Vanadium oxide is a well-known catalyst in reduction of NO_x , NH_3 .^{18,19} Theoretical framework for ammonia adsorption on vanadium oxide also is available.^{20,21} Moreover there are also some reports which have indicated role of RuO_2 in increasing the sensitivity of tin oxide towards ammonia.²² Ruthenium nanoparticles are likely to be covered with thin oxide layer. Therefore we have chosen to use ruthenium decorated V_2O_5 as a novel sensor for ammonia detection.

Ever increasing ammonia level in atmosphere as well as water is of great concern. Ammonia level from few ppb to tens of ppb in air is permissible. Ammonia is released by various rural and urban human activities like agriculture (use of fertilizers), husbandry, chemical industry, cold storage or refrigeration plants of food storage steadily causing increase of ammonia in air. Small quantities of dissolved ammonia in water can become threat to marine life. Continuous inhaling up to 35 ppm for 15 minutes and maximum 8 h exposure at 25 ppm is just safe according to the US Agency for Toxic Substances and Disease Registry (ATSDR CAS # 7664-41-7). Major threat of ammonia can be from industrial places and large cold storages of food as is evident from major accident like West Texas Fertilizer (USA) plant in 2013 which not only completely destroyed the establishment but also killed many lives. A similar accident took place in 2017 at a cold storage in Kanpur, India killing at least five workers. Recently, in 2019 also ammonia leakage is reported in Lucknow, India. Thus it is very important to

^aCentre for Materials for Electronics Technology (C-MET), Panchwati, Off Pashan Road, Pune-411008, India. E-mail: adhyapak@cmet.gov.in; Fax: +91-20-25898180; Tel: +91-20-25899273

^bInternational Advanced Research Centre for Powder Metallurgy and New Materials, Hyderabad-500005, India

^cSavitribai Phule Pune University, Pune-411007, India

control leakage of ammonia in its early stage. Proper alarm systems must be equipped with appropriate sensors *i.e.* fast response time and recovery time, selectivity, reproducible as well as operating at low temperature, preferably room temperature. Room temperature operation eliminates the cost of electricity needed for heating the sensor as well as avoids catching fire in case of any accidental explosion in its neighborhood.

There are some reports on the use of V_2O_5 as an ammonia gas sensor.^{10,12,17} However, the sensitivity of V_2O_5 towards ammonia is usually low and response as well as recovery times are large. Surface sensitization is often made to increase the sensing of V_2O_5/VO_2 by using noble metals or graphene.^{3,13,23,24} Some nanocomposites also have been reported.^{25–28} V_2O_5 has also been deposited by many groups in porous silicon structure.^{29–31} Novel assemblies of V_2O_5 have been reported by Wang *et al.* which improved the hydrogen gas sensing activity.² The attempts using graphene functionalized V_2O_5 could improve the sensitivity towards NH_3 gas but response and recovery times were still few tens of seconds.³

Here we report, a facile method using hydrothermally synthesized V_2O_5 decorated with ruthenium nanoparticles (1% $Ru@V_2O_5$), which serves as a highly sensitive and selective sensor with 0.52 s @ 130 ppm and 1.57 s @ 10 ppm, response time for ammonia. The recovery times are 15.13 s @ 130 ppm and 9.39 s @ 10 ppm. This novel ruthenium nanoparticles decorated vanadium oxide sensor is capable of operating at room temperature. The sensitivity of the sensor is $\sim 4\%$ for 130 ppm of ammonia, which is quite good for V_2O_5 ammonia sensor.

Field Emission Scanning Electron Microscopy (FE-SEM) images revealed that V_2O_5 had poly-dispersed microparticles having layered structure. 1% $Ru@V_2O_5$ had a more interesting morphology. One could clearly see that some Ru nanoparticles were decorated on the layered V_2O_5 microparticles. Energy Dispersive Analysis of X-rays (EDAX) of both V_2O_5 and 1% $Ru@V_2O_5$ also was carried out for determining the composition of the sample along with the presence of any contamination in the samples. Transmission Electron Microscopy (TEM) images also clearly showed presence of ruthenium particles on the V_2O_5 surface of 1% $Ru@V_2O_5$ sample. Further analysis using High Angle Annular Dark Field (HAADF) and Scanning Transmission Electron Microscopy (STEM) also was carried out to record more morphological, structural as well as compositional details. V_2O_5 had orthorhombic and ruthenium particles had hexagonal structure, as found from X-ray Diffraction (XRD) analysis. Sensitivity analysis was carried out by measuring the changes in the resistance of the samples with or without the presence of ammonia. X-ray Photoelectron Spectroscopy (XPS) analysis was carried out to find out the elemental composition as well as oxidation states of vanadium, ruthenium and oxygen in the samples under investigation.

2 Materials and methods

2.1 Materials

All A. R. grade reagents were used for the synthesis of materials. Ammonium vanadate, NH_4VO_3 , (May and Baker laboratory chemicals, 99.0%), maleic acid ($HO_2CCHCHCO_2H$, 99.0%), and

polyethylene glycol ($C_{2n}H_{4n+2}O_{n+1}$), PEG-400, (S.D fine chemicals), absolute ethanol (99.9%), ruthenium chloride hydrate $RuCl_3 \cdot xH_2O$ (Sigma Aldrich 98%), hydrazine hydrate, H_6N_2O (Loba chemie, 99.0%) and deionised water were used in the experiment (Scheme 1).

2.2 Synthesis of V_2O_5


Synthesis of V_2O_5 was performed by hydrothermal method as follows. 1 mole of maleic acid (surfactant) was dissolved in PEG-400-water mixture (1 : 10). Further, 0.5 mole of NH_4VO_3 was dissolved separately in 50 mL of deionized water. This solution was added dropwise to the maleic acid and PEG-water solution under constant stirring, which then turns from a colourless solution to orange solution. After complete addition, the solution was stirred for about 2 h at room temperature ($\sim 30^\circ C$). This reaction mixture was then transferred into 250 mL Teflon lined stainless steel autoclave, kept at $180^\circ C$ for 24 h. After this, autoclave was cooled to room temperature. Black precipitate was obtained when the solution was centrifuged at ~ 5000 rpm for 15 min. The precipitate was then washed several times with deionized water and finally with ethanol. It was dried at $60^\circ C$ for 4–5 h. The dried product was calcined at $500^\circ C$ for 3 h. This resulted into a yellowish orange V_2O_5 powder.

2.3 Synthesis of 1% $Ru@V_2O_5$

Precursor $RuCl_3$ (0.0102 g) was taken in a beaker and 30 mL of deionised water was added in it with continuous stirring till it was completely dissolved giving a clear solution. V_2O_5 (0.4897 g) was then added to the above solution. In another beaker 1 mL of hydrazine hydrate was mixed in 19 mL deionized water and the solution was dropwise added to the precursor solution till it changed to olive green colour. The supernatant was removed and precipitate was dried at $60^\circ C$ for 3 h, which resulted into an olive green powder.

2.4 Material characterization

The structural analysis of the V_2O_5 and 1% $Ru@V_2O_5$ was made using X-ray diffraction (XRD) technique. Rigaku Miniflex X-ray

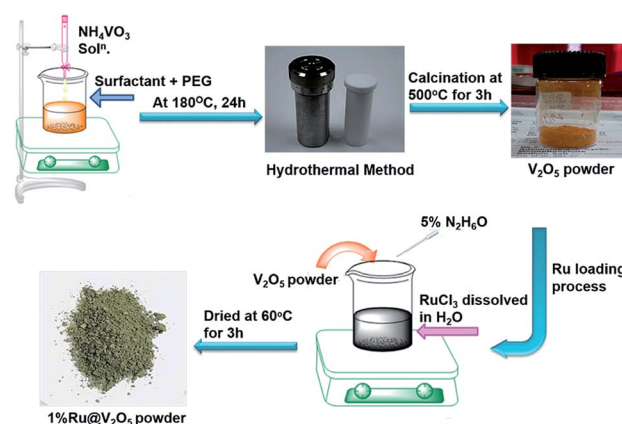

Scheme 1 Schematic representation of V_2O_5 and 1% $Ru@V_2O_5$ synthesis.



diffractometer equipped with copper target ($\text{CuK}\alpha$, $\lambda = 1.5406 \text{ \AA}$) and nickel filter was used to record the diffraction patterns. Powder samples were held on glass substrates.

Field Emission Scanning Electron Microscopy (FE-SEM) was performed with a JEOL-JSM Model 6700F having Energy Dispersive Analysis of X-rays (EDAX) attachment. For the analysis, silicon substrates were used on which a thin layer of powder samples was spread. Transmission Electron Microscopy (TEM) analysis of V_2O_5 and $1\%\text{Ru@V}_2\text{O}_5$ samples was carried out using TEM 2200FS JEOL, equipped with High Angle Annular Dark Field (HAADF) and Scanning Transmission Microscopy (STEM) facilities, operated at 200 keV electron energy. The samples were prepared by putting a drop of solution containing samples on copper grids.

The reflectance spectra were recorded on Jasco-V-770 spectrophotometer. The samples were pressed in a quartz sample holder cavity and measurements were done in the spectral range 200 to 1200 nm.

Fourier transform infrared spectroscopy (FTIR) analysis of V_2O_5 and $1\%\text{Ru@V}_2\text{O}_5$ samples was carried out using a Bruker TENSOR37. Samples were kept in the stainless steel sample holder for measurements in the range from 400 to 4000 cm^{-1} .

X-ray Photoelectron Spectroscopy (XPS) analysis was carried out using ESCA + model of Omicron, UK. $\text{AlK}\alpha$ (X-ray energy 1253.6 eV) was used as the source of X-rays. Photoelectron spectra were recorded using hemispherical analyzer held at 50 eV pass energy and CASA XPS software was used for the analysis of the spectra.

2.5 Fabrication and sensing measurements

Sensing measurements on V_2O_5 and $1\%\text{Ru@V}_2\text{O}_5$ samples were performed in a static system (shown in Scheme 2) as per the procedure reported earlier.³² Briefly it is made of an airtight glass dome with inlet and outlet for gases/vapors. The vapors can be injected using a syringe through a metallic tube connected to the steel base plate of the glass dome. A water suction pump is used to remove the gases from the chamber. There is

a provision of heater along with thermocouple at the base of the dome. The alumina substrate (0.6 mm thick and $10 \times 10 \text{ mm}$ area) was used for the fabrication of interdigitated electrode (IDE) made up of silver that occupies an area of $8 \times 8 \text{ mm}$. The width of the digits is 1 mm and the space between them is 0.5 mm. The IDE is kept on the heater and connected to a Keithley Digital Multimeter (model DMM 7510, $7\frac{1}{2}$ Digital multimeter) equipped with computer. The change in resistance with time was recorded on computer with KickStart software.




For sensing measurements, the sample is coated on IDE. The gases/vapors are injected through the syringe and corresponding change in resistance is measured. After stipulated time the resistance value starts dropping down due to desorption of gases. Then the desorbed gas is driven out of the chamber by using a water suction pump. Sensitivity of the sample can be then determined by finding out the change in the resistance from ambient and that occurs when the film is in contact with a gas. Thus, initial (in ambient air) resistance of the thin film is R_a and that in the contact with a test gas is R_g then the percentage sensitivity or the gas response $S\%$ can be calculated with the equation,

$$S\% = \left| \frac{R_a - R_g}{R_a} \right| \times 100\% \quad (1)$$

In these experiments various oxidizing gases such as SO_2 , NO_x and reducing vapors like $\text{C}_2\text{H}_6\text{O}$ (ethanol), CH_4O (methanol), $\text{C}_3\text{H}_6\text{O}$ (acetone), CH_2O (formaldehyde), NH_3 (ammonia), $\text{C}_6\text{H}_{15}\text{N}$ (triethylamine), $\text{C}_3\text{H}_9\text{N}$ (trimethylamine) were used.


3 Results and discussion

'As received' pristine V_2O_5 powder resulting from the hydrothermal synthesis was yellowish orange in color, characteristic of V_2O_5 . The hydrothermal synthesis of V_2O_5 can be explained using following eqn (2)–(5).³³



There are three polymorphs of V_2O_5 viz. α - V_2O_5 , β - V_2O_5 and γ - V_2O_5 having same yellowish orange color.^{34,35} The differences in the polymorphs arise due to their structures viz. their lattice parameters as well as the way in which the V_2O_5 pyramids are oriented or stacked. In α - V_2O_5 , $a = 11.516 \text{ \AA}$, $b = 3.5656 \text{ \AA}$ and $c = 4.3727 \text{ \AA}$ [JCPDS card # 41-1426]. Whereas in β - V_2O_5 , $a = 7.1140 \text{ \AA}$, $b = 3.5718 \text{ \AA}$ and $c = 6.2846 \text{ \AA}$.²⁰ β - V_2O_5 is metastable at room temperature and can be observed under high pressure. γ - V_2O_5 crystallizes with lattice parameters $a = 9.9461 \text{ \AA}$, $b = 3.5852 \text{ \AA}$ and $c = 10.0423 \text{ \AA}$.²⁰

As discussed in the introduction, the formation of vanadium oxides depends on the synthesis and processing procedure as

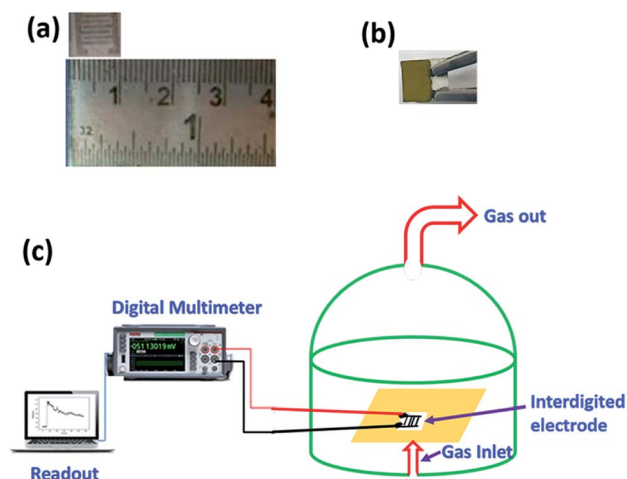

Scheme 2 Photograph of (a) interdigitated electrode (IDE) (b) sample coated on the IDE (c) schematic representation of sensing set up.



well as precursors used. Therefore, we characterized the V_2O_5 powder using XRD. Lower curve in Fig. 1(a) illustrates the XRD pattern of the V_2O_5 sample synthesized here. It is in good agreement with the JCPDS card # 41-1426 for orthorhombic α - V_2O_5 . This is also confirmed by the characteristic FTIR spectrum shown in Fig. 1(b). It was discussed by Pinna *et al.* that the absorption peak around 1009 cm^{-1} in FTIR, assigned to $V=O$ stretching, splits into two components in γ - V_2O_5 .³⁶ Absence of such splitting in the peak at 1009 cm^{-1} confirms the assignment using XRD that the sample is indeed in α - V_2O_5 phase. We can also see that all the peaks of α - V_2O_5 appear in the sample without any peaks due to contaminants. Thus we have obtained a good quality α - V_2O_5 polycrystalline sample.

XRD pattern (upper curve) of $1\%Ru@V_2O_5$ is also shown in Fig. 1(a). It is noticed that all the peaks of V_2O_5 are present along with two more peaks. These new peaks are due to (100) and (102) of hexagonal phase of ruthenium in agreement with (JCPDS card # 01-1256) for ruthenium. Careful analysis of XRD pattern suggests that these peaks belong to metallic ruthenium and there is no indication of any oxide formation. However, from XRD alone the possibility of any ruthenium oxide or sub-oxide on the surface as a thin layer cannot be confirmed.

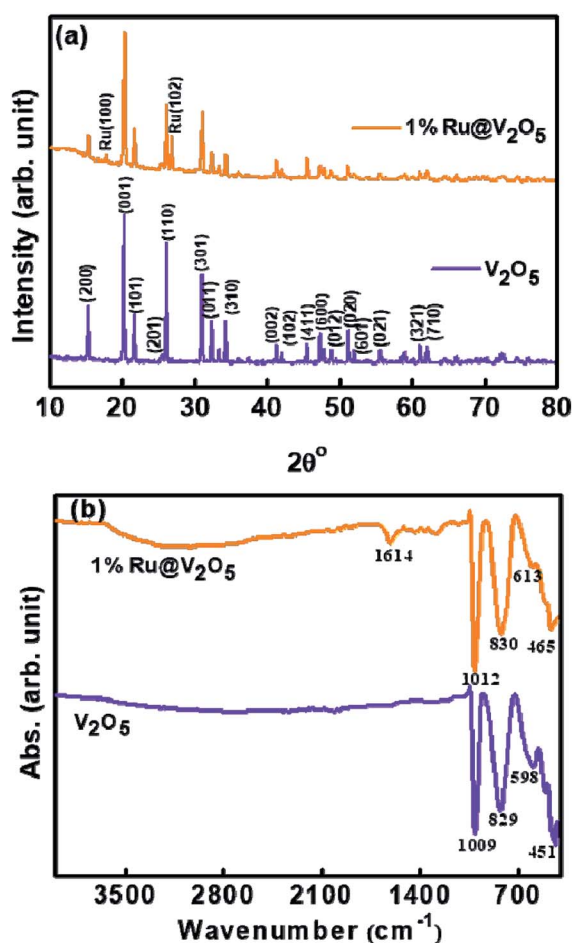


Fig. 1 (a) X-ray diffraction and (b) FTIR of V_2O_5 and $1\%Ru@V_2O_5$ powders.

Fig. 1(b) shows FTIR spectra of as-synthesized V_2O_5 (lower curve) and $1\%Ru@V_2O_5$ (upper curve) samples. In case of pristine V_2O_5 there are four peaks located at 451, 598, 829 and 1009 cm^{-1} , which are characteristic peaks of orthorhombic V_2O_5 .¹

The peaks observed at 451 and 598 cm^{-1} correspond to symmetric and asymmetric vibrations of triply coordinated oxygen, whereas peaks located at 829 and 1009 cm^{-1} correspond to vibrations of bridge oxygen and stretching vibrations of $V^{5+}=O$ respectively. It is observed that the peak at 829 cm^{-1} in FTIR of the pristine V_2O_5 is only slightly shifted to 830 cm^{-1} in case of $1\%Ru@V_2O_5$ sample. But the peaks at 451, 598 and 1009 cm^{-1} shift by larger amount to 461, 613 and 1012 cm^{-1} respectively in $1\%Ru@V_2O_5$ sample. The shift in the wavenumber to higher value here indicates that there are small bond length decreases in V_2O_5 due presence of Ru. Additionally, in case of $1\%Ru@V_2O_5$ two new peaks, one sharp at 1614 cm^{-1} and one very broad peak centered at $\sim 3000\text{ cm}^{-1}$ can be seen. The peak at 1614 cm^{-1} has been identified as hydrogen bonded surface water molecule.³⁷ The peak centered around 3000 cm^{-1} can be attributed to adsorbed water molecules. The absence of peaks around 3000 cm^{-1} and 1614 cm^{-1} on pristine V_2O_5 surface are consistent with the theoretical calculations of Yin *et al.* which show that water adsorption is possible on V_2O_5 surface but water dissociation does not take place on V_2O_5 .³⁸

Fig. 2 depicts the FE-SEM patterns of V_2O_5 and $1\%Ru@V_2O_5$. The V_2O_5 sample in Fig. 2(a) and $1\%Ru@V_2O_5$ in Fig. 2(b) show formation of large, irregular flakes of couple of micrometer sizes with layered structure. EDAX (not shown here) analysis revealed that V is 8.82 at% and O is 91.82 at% in V_2O_5 . No impurities were detected in EDAX. In case of $1\%Ru@V_2O_5$, although there is a presence of ruthenium, we do not clearly see the ruthenium particles in the FESEM images. Therefore, we performed TEM analysis of the V_2O_5 and $1\%Ru@V_2O_5$ samples.

The TEM images of V_2O_5 and $1\%Ru@V_2O_5$ are shown in Fig. 3. In Fig. 3(a) one can see a number of particles of few hundreds on nm in agreement with FESEM of Fig. 2(a) for V_2O_5 . The typical lattice fringes (Fig. 3(b)) show d spacing of 0.40 nm which is the lattice spacing in (001) set of planes for V_2O_5 . Electron diffraction pattern of V_2O_5 as obtained from TEM is illustrated in Fig. 3(c). The intense diffractions spots without

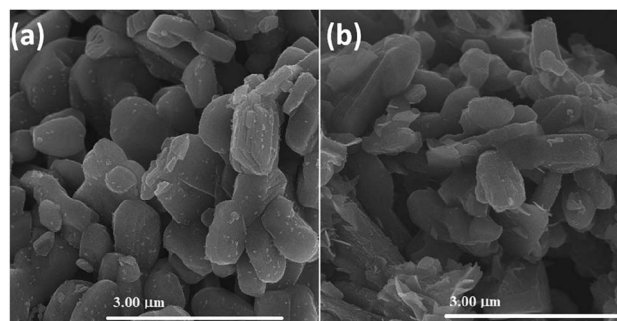


Fig. 2 FE-SEM images of (a) V_2O_5 and (b) $1\%Ru@V_2O_5$.



any rings indicate that there are single crystalline particles present in the V_2O_5 sample. The middle panel of Fig. 3 shows the TEM images of $1\%Ru@V_2O_5$. Fig. 3(d) shows the image of a typical particle in which particle surrounded by nanoparticles can be seen. For the sake of the guideline to the eye, the surface region with numerous particles is shown with the dotted lines. Using digital micrography software the ruthenium nanoparticle sizes were found to be 10–20 nm. The lattice fringes observed in Fig. 3(e) with lattice spacing ~ 0.22 nm could be assigned to Ru (100) planes. A diffraction pattern in Fig. 3(f) shows well defined diffraction spots. Ru (100) spots could be identified in Fig. 3(f). Hexagonal structure of ruthenium also is clearly observed in this pattern. Thus the surface of V_2O_5 particles is decorated with crystalline ruthenium nanoparticles. The EDAX pattern in Fig. 3(g) also shows presence of ~ 1.51 at% ruthenium in $1\%Ru@V_2O_5$ sample. Vanadium and oxygen at% is 76.35 and 22.14 respectively.

Fig. 4(a) shows the representative HAADF image of an edge of a $1\%Ru@V_2O_5$ sample. Particles can be clearly seen but to know their composition corresponding elemental mapping was performed and shown in Fig. 4(b–d). The elemental mapping of 1%

$Ru@V_2O_5$ reveals the distribution of O (green color) V (red color) and Ru (greenish blue). It is observed that at the edges of the flake, ruthenium particles are concentrated. Fig. 4(e) is the overlay of O, V and Ru in Fig. 4(b–d). It can be seen that except for the colors it is similar to Fig. 4(a), a TEM image of the same portion of the sample.

Presence of ruthenium in case of $1\%Ru@V_2O_5$ is accompanied by change in the resistance. At room temperature, the resistance of the V_2O_5 thin films used in the sensing measurements was found to be 67.09 k Ω but that of $1\%Ru@V_2O_5$ was 20.71 k Ω . This dramatic reduction of resistance of thin films of material with same dimensions indicates that metal deposition is responsible in reducing the resistance of $1\%Ru@V_2O_5$ by such a large value. The changes are also accompanied by band gap reduction of $1\%Ru@V_2O_5$ as compared to pristine V_2O_5 sample. This is clearly seen in Fig. 5(a) optical absorption spectra (b) reflectance spectra (c and d) corresponding Kubelka–Munk function plots of both the samples. Kubelka–Munk k/f function is calculated using formula,

$$k = (\text{intensity}/100)^2, f = \text{intensity}/100 \quad (6)$$

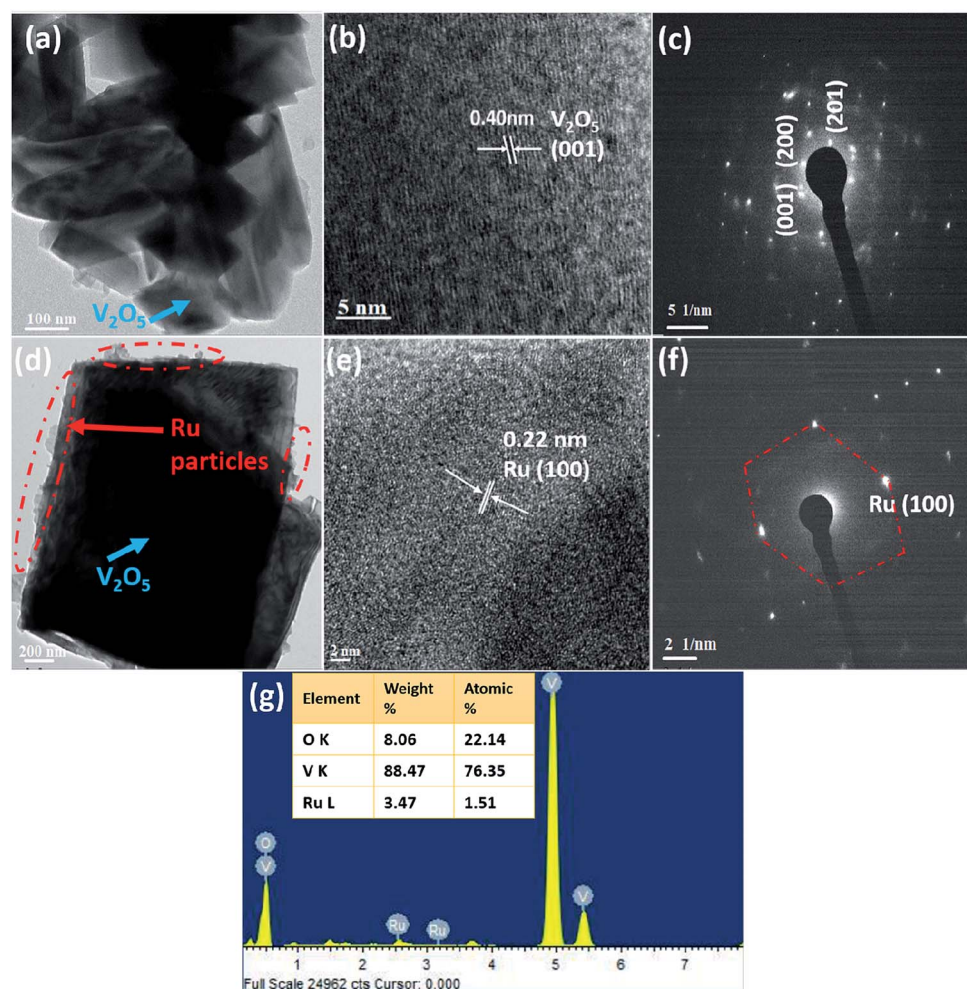


Fig. 3 FE-TEM analysis (a) overview image of V_2O_5 particles (b) lattice resolved image of V_2O_5 (c) electron diffraction of V_2O_5 (d) a single particle of $1\%Ru@V_2O_5$ (e) lattice resolved image of $1\%Ru@V_2O_5$ (f) electron diffraction of $1\%Ru@V_2O_5$ (g) EDAX of $1\%Ru@V_2O_5$.



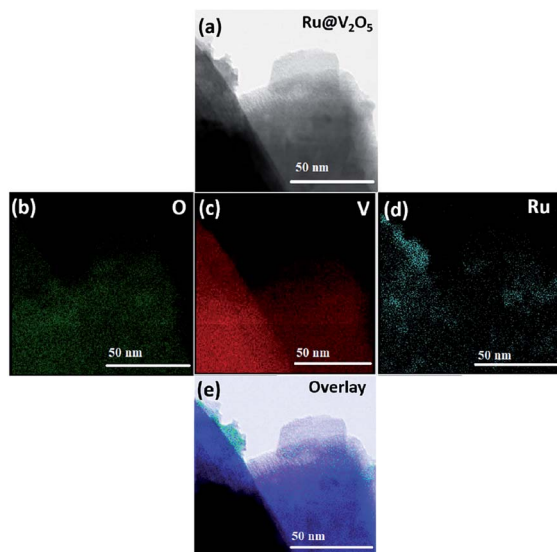


Fig. 4 (a) HAADF-STEM image of an edge portion of a 1%Ru@V₂O₅ particle (b) elemental mapping of oxygen (c) elemental mapping of vanadium (d) elemental mapping of ruthenium (e) overlay image of oxygen, vanadium and ruthenium.

In Fig. 5 the extrapolation of the leading edges to x-axis gives the energy gap. The energy gap for the V₂O₅ sample using Kubelka–Munk function is 2.20 eV. This is in close agreement with the value reported for V₂O₅.^{39,40} The energy gap was found to be 2.15 eV for 1%Ru@V₂O₅. Thus band gap for 1%Ru@V₂O₅ has decreased by 0.05 eV. Moreover the band edge for 1%Ru@V₂O₅ is not as sharp as that for V₂O₅ and is tailing even beyond 2 eV, probably due to increase in diffuse interface (presence of particles at the surfaces in case of 1%Ru@V₂O₅). In any case, it can be deduced that ruthenium has substantially influenced the V₂O₅ sample and probably is responsible for the

reduction in the resistance of the sample. As we will see below, such changes in the material are also responsible for the sensing change of 1%Ru@V₂O₅ sample compared to V₂O₅.

Many transition metal oxide sensors operate effectively at high temperature. This can be attributed to the higher reaction rates at high temperature as well as increased conductivity of metal oxides at high temperatures due to the formation of oxygen defects. We therefore first made the sensitivity measurements for both V₂O₅ and 1%Ru@V₂O₅ samples at three temperatures *viz.* room temperature (30 °C), 50 °C and 100 °C. After measuring the initial resistances of the samples at these temperatures in air (R_a , without any gas injection in the chamber) the changes in the resistances in presence of different gas ambient (R_g) at these temperatures for fixed quantity *viz.* 130 ppm, were measured. Literature on V₂O₅ semiconductor shows interesting resistivity behavior. It is p-type, n-type or even shows transition from n to p or *vice a versa*.^{9,14} An n-type semiconductor shows reduction in the resistance in presence of a reducing gas. Here we have used vapors of ethanol, methanol, acetone, formaldehyde, ammonia, triethylamine and trimethylamine as reducing gases. We also checked the sensing for the oxidizing gases SO₂ and NO_x.

Fig. 6(a) shows the sensitivity obtained using the sensitivity equation,¹ at three temperatures *viz.* room temperature (30 °C), 50 °C and 100 °C for various gases at 130 ppm. Similarly sensing measurements were carried out for the sample 1%Ru@V₂O₅ and shown in Fig. 6(b). A dramatic difference is seen for the sensing of all the gases investigated here as seen in Fig. 6(b) when V₂O₅ is replaced with 1%Ru@V₂O₅. First of all there is an overall increase in the sensitivities at room temperature for all the gases. But more striking change occurs for NH₃ vapor sensing and will be the focus of our discussion. It can be seen from Fig. 6(b) that the sensitivity of ammonia has increased to ~4% at room temperature. This probably is the highest value obtained so far for any functionalized or nanocomposite or

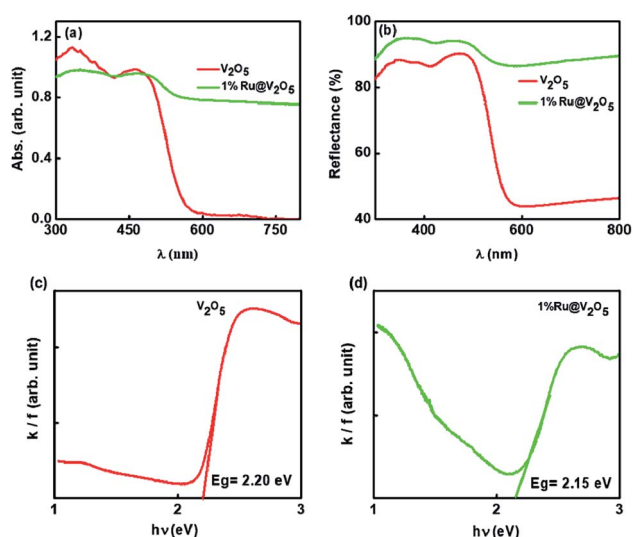


Fig. 5 (a) Optical absorption spectra (b) reflectance spectra (c and d) corresponding k/f vs. $h\nu$ Kubelka–Munk plots of V₂O₅ and 1%Ru@V₂O₅.

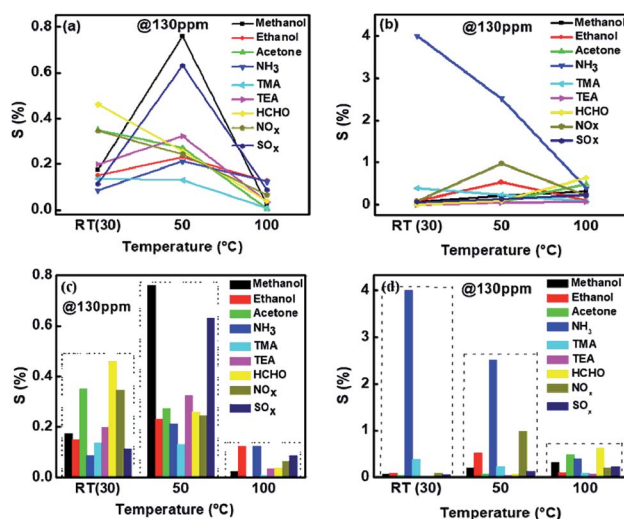


Fig. 6 Comparison of (a) sensitivity of V₂O₅ and (b) 1%Ru/V₂O₅ towards different gases. Sensitivity shown as bar graph, at different temperatures, for (c) V₂O₅ and (d) 1%Ru/V₂O₅.



otherwise modified V_2O_5 sample, with exception of graphene composites. With increase of temperature to 50°C , sensitivity of $1\%\text{Ru@V}_2\text{O}_5$ towards NH_3 reduced to $\sim 3\%$ and then further went to its lowest value of $\sim 0.5\%$ at 100°C . Corresponding bar graphs for V_2O_5 and $1\%\text{Ru@V}_2O_5$ are illustrated in Fig. 6(c) and (d) respectively. From Fig. 6(d) one can see that sample $1\%\text{Ru@V}_2O_5$ shows remarkable sensitivity at room temperature and it is very selective. For $1\%\text{Ru@V}_2O_5$ the response to other gases is relatively negligible ($<0.5\%$).

This makes $1\%\text{Ru@V}_2O_5$ a very good ammonia sensor in terms of selectivity and sensitivity at room temperature. Obtaining room temperature operating sensor is very important as it can be used in places where the gas needs to be stored at high pressure and needs to be detected for any leaks. Particularly in case a gas cylinder containing ammonia gas explodes it can lead to a disaster, as it is a toxic gas. Operation at high temperature of sensors can not only be expensive but also dangerous as gases can further catch fire on exploding.

Before proceeding with further analysis of $1\%\text{Ru@V}_2O_5$, we measured the effect of humidity on $1\%\text{Ru@V}_2O_5$. This is particularly essential when a sensor is to be used at room temperature, as in many places there can be large humidity at room temperature. It can be seen from Fig. 7 that over the entire range, less than 0.1% contribution can come from humidity. Thus the effect of humidity on our measurements is negligible.

As the sensitivity for NH_3 was found to be highest and sensor was also selective, further measurements were made on NH_3 interaction with $1\%\text{Ru@V}_2O_5$. Fig. 8 shows the sensitivity plot for NH_3 for the fixed concentration of NH_3 on $1\%\text{Ru@V}_2O_5$. It can be seen that the repeatability of the material is quite good. Also the sensor shows instantaneous response and recovery without any saturation.^{41–43}

Further we show the response of the sensor for different concentrations of ammonia in Fig. 9(a). It can be seen that the sensitivity decreases with reduction in the gas concentration. The sensitivity with different NH_3 concentrations can be seen from Fig. 9(b) is linear on the log-log scale over the entire range (10–130 ppm) investigated here. Use of log-log scale has been made earlier for plotting the sensitivity.^{44,45}

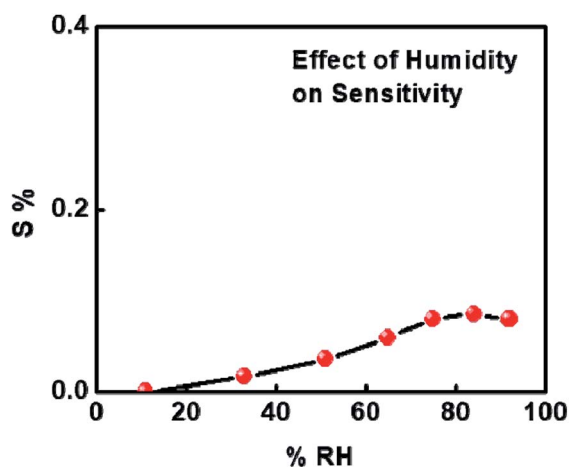


Fig. 7 Humidity sensing of $1\%\text{Ru@V}_2\text{O}_5$.

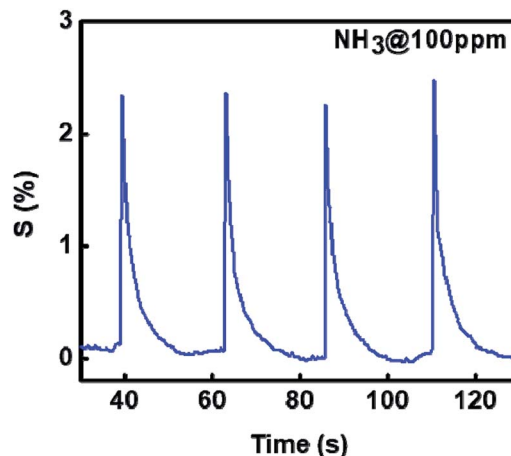


Fig. 8 Sensitivity of $\text{Ru@V}_2\text{O}_5$ as a function of time at constant NH_3 concentration (100 ppm), shown for 4 cycles.

We have also determined the response time and recovery times for each concentration from Fig. 9(a). It is also enlarged and shown for one concentration in the inset of Fig. 9(a). The response time is considered as the time required to reach the lowest resistance in the presence of gas and recovery time is taken as the time needed to attain the 90% of the original value of resistance *viz.* R_a .

Fig. 10(a) shows the dynamic response and recovery time for 100 ppm towards ammonia gas at room temperature. In Fig. 10(b) we have plotted response and recovery time for each

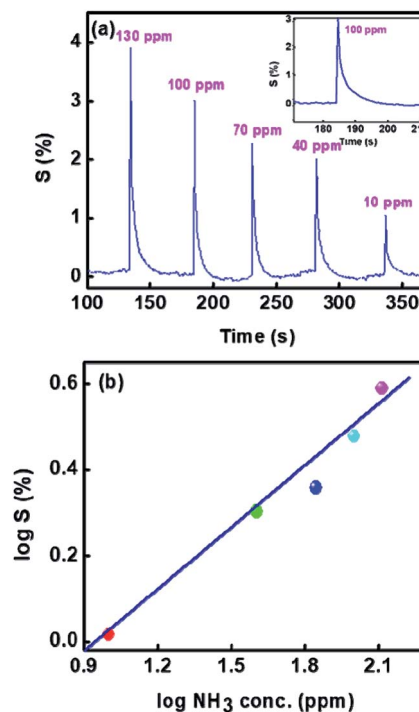


Fig. 9 Sensitivity of $1\%\text{Ru@V}_2\text{O}_5$ (a) as a function of time for various concentrations of NH_3 and (b) log-log plot of sensitivity vs. ammonia concentrations.




concentration (obtained from Fig. 9(a)). As can be seen from Fig. 10(b), the maximum response time is less than 2 seconds and the recovery time is less than 12 seconds. These to our knowledge are the best response and recovery times for V_2O_5 sensor so far. For comparison see Table 1, where we have listed the ammonia sensing data of different V_2O_5 morphologies and also the temperatures or concentrations.

3.1 Ammonia sensing mechanism of V_2O_5 and 1%Ru@ V_2O_5



Vanadium pentoxide (V_2O_5) is a very common and stable oxide (melting point 690 °C). It is known to be a good catalyst, particularly for selective catalytic reduction of NO_x along with NH_3 .^{52–54} V_2O_5 (010) surface of orthorhombic V_2O_5 is commonly studied theoretically, as it is found to be most important and exposed surface in most of the catalytic reactions.⁵⁴ Interaction of NH_3 with V_2O_5 (010) also has been studied theoretically.^{38,55} It was found that NH_3 adsorbs preferentially on three Brønsted sites shown in Fig. 11 which is constructed based on the Fig. 1 from the work of Yin *et al.*³⁸ Accordingly, three oxygen atoms have been identified *viz.*, O1, O2, O3 and two types of vanadium V_1 , V_2 on bare (010) surface.³⁸ They find that adsorption probability on $O1H > O2H > O3H$ sites. As H_2O cannot dissociate on bare V_2O_5 they had assumed that already atomic hydrogen (H) was present on these sites so that NH_4^+ formation could take place.

On Lewis sites adsorption of NH_3 is in any case less but it was necessary that presence of hydrogen atom on oxygen or bonding with oxygen was necessary for the formation of NH_4^+ species.

Here we do not further discuss exact charge transfers *etc.* between NH_3 and H or vanadium at different sites which are discussed in ref. 38 and 55 but only use their conclusions *viz.* hydrogen atom needs to be present at Brønsted site and adsorption of NH_3 to form NH_4^+ is preferentially on $O1 > O2 > O3$ site with more charge transfer to surface at $O1 > O2 > O3$ sites.³⁸ Assuming the formation of NH_4^+ one can write,



Here, hydrogen (H^+) is provided by 1%Ru/ RuO_2 , nanoparticles on 1%Ru@ V_2O_5 . However, different reaction pathways are possible as discussed by Modafferi *et al.*¹² as given below,



For reaction pathways (8) and (9) presence of adsorbed oxygen is necessary. Which reaction pathway among (7)–(9) is chosen is difficult to decide here, as this would need *in situ* determination of released gas species in the reaction (which is not possible here).

It can be seen in Fig. 1(b) that V_2O_5 does not show any prominent OH related vibrational mode over a wide range from 4000 cm^{-1} to 450 cm^{-1} . However, as was discussed with reference to Fig. 1(b), 1%Ru@ V_2O_5 does have this possibility.

FTIR spectrum clearly shows a sharp vibrational mode at 1614 cm^{-1} and a broad band around 3000 cm^{-1} indicative of the presence of dissociated water molecules.^{35,37}

Presence of ruthenium in 1%Ru@ V_2O_5 is also evident from XPS. XPS is a versatile technique to know the oxidation states or charge transfers between the surface atoms. The XPS peak shift to higher binding energy when charge from the corresponding atom is removed and peak shifts to lower binding energy if it gains the more charge. This type of charge transfer takes place amongst the neighboring atom.

In Fig. 12(a) the survey scans for V_2O_5 and 1%Ru@ V_2O_5 are shown. One can see that in V_2O_5 sample only vanadium, oxygen and carbon related peaks are present, suggesting that the sample is free of any impurities. The 1%Ru@ V_2O_5 has slight indication of additional peak of N 1s at ~400 eV. In Fig. 12(b) the plots are made of narrow region from 276 to 294 eV. The V_2O_5 spectrum in the carbon region is deconvoluted into three peaks positioned at 284.6 eV (C_1), 286.7 eV (C_2) and 288.5 eV (C_3) eV, all due to C 1s. The peak at 284.6 eV is assigned to adventitious carbon and treated as the reference for the whole analysis. C_2 and C_3 can be identified as due to C–O and C=O respectively. In the same spectral region for the 1%Ru@ V_2O_5 sample we observe that there also C 1s peak has C_1 , C_2 and C_3 components present but there are two additional peaks, which can be fitted. These can be identified as spin–orbit split Ru $3d_{5/2}$ at 282.2 eV and Ru $3d_{3/2}$ at 286.0 eV positions. The binding energy of Ru $3d_{5/2}$ and Ru $3d_{3/2}$ as well as their spin–orbit splitting of 3.8 eV suggests that Ru is in the Ru^{3+} state.^{56,57} The Ru $3d_{5/2}$ and Ru $3d_{3/2}$ peaks are separated by 3.8 eV in close agreement with reference handbook, which showed the splitting to be 4.1 eV for

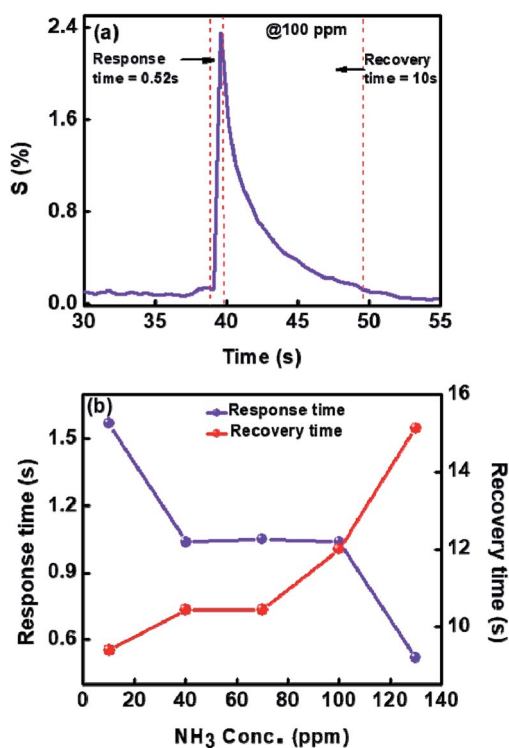


Fig. 10 (a) Dynamic response to NH_3 (b) response and recovery times of 1%Ru@ V_2O_5 at 30 °C for different concentrations of NH_3 gas.



Table 1 List of reports on ammonia sensing using various V_2O_5 morphologies

| Sr. no. | Metal oxides used | Gas detected | Sensitivity (%) | Operating temperature ($^{\circ}\text{C}$) | Response/recovery time | Ref. |
|---------|---|---|------------------------|--|--|--------------|
| 1 | V_2O_5 nanorods | Ethanol (100 ppm) Ammonia (100 ppm) | 1.03 1.018 | RT | 2.5 s (res. time from graph) 5 s (res. time from graph) | 10 |
| 2 | V_2O_5 /PVAC-fibres | Ammonia (0.8–8.5 ppm) | 30 (from graph) | 200–250 | 50 s/350 s | 12 |
| 3 | V_2O_5 nanofibers | 1-Butylamine (10 ppm) Ammonia (10 ppm) | 42 1.8 | RT | Not mentioned | 17 |
| 4 | V_2O_5 @ TiO_2 | Ammonia (5 ppm) | 60 | 365 | 9 s/6 s | 46 |
| 5 | 2 wt% Sn doped V_2O_5 nanoparticle | Ammonia (5–50 ppm) | 77.84 at 50 ppm | RT | Not mentioned | 47 |
| 6 | V_2O_5 /PVP | Ammonia (0.1–0.8 ppm) | 6 (0.8 ppm) from graph | 260 | 25 s/60 s (from graph) | 48 |
| 7 | V_2O_5 - WO_3 - TiO_2 (potentiometric sensor) | Ammonia (10–320 ppm) | Not mentioned | 550 | 5–8 s/8–12 s | 49 |
| 8 | V_2O_5 /PANI amperometric sensor | Ammonia (0–54 ppm) | 175 (from graph) | Not mentioned | 45 min/60 min (from graph) | 50 |
| 9 | pTSA doped V_2O_5 @PANI nanofibers | Ammonia (0.1 M) | Not mentioned | RT | 1 min/1.5 min (from graph) | 18 |
| 10 | $V_2O_5 + V_7O_{16}$ | Ammonia (200 ppb) | Not mentioned | 350 | 60 m/60 min (from graph) | 19 |
| 11 | V_2O_5 nanopillars | Ammonia (2.5–20 ppm) | Not mentioned | 350 | 15 min/15 min (from graph) | 21 |
| 12 | $V_2O_5 + V_7O_{16}$ | Ammonia (1 ppm) | 32 (from graph) | 350 | 10 min/10 min (from graph) | 22 |
| 13 | $V_2O_5 + V_7O_{16}$ | Ammonia (40 ppb) | Not mentioned | 350 | 10 min/10 min | 51 |
| 14 | 1%Ru@ V_2O_5 | Ammonia (10 ppm) | 4 | RT | 1.5 s/9.3 s | Present work |

Ru metal. This suggests that ruthenium is forming RuO_2 layer. Ru is probably forming contact with the V_2O_5 (also evident from STEM in Fig. 4). Schematic diagram depicting this is given in Fig. 12 and discussed later. From TEM we know that ruthenium nanoparticles of ~ 10 – 20 nm size are formed on V_2O_5 . Penetration depth of XPS is ~ 2 – 3 nm. Therefore these particles could have ruthenium metal inside with thin layer of ruthenium oxide as suggested from XPS here but also consistent with the Ru metal peaks observed in Fig. 1, in XRD of 1%Ru@ V_2O_5 . Considering that XPS signal appears from very shallow surface (< 3 nm) it can be safely assumed that RuO_2 is present along with the underneath ruthenium metal in the hexagonal phase.

In Fig. 12(c) vanadium and oxygen region is plotted from 510 to 540 eV. We can clearly see two peaks at 517.3 eV and 524.6 eV which can be assigned to $2p_{3/2}$ and $2p_{1/2}$ of V^{5+} state.⁵⁶ The other

two peaks at 530.3 eV and 532.1 eV, could be due to oxygen and molecularly adsorbed H_2O respectively. For 1%Ru@ V_2O_5 also two peaks can be fitted for $2p_{3/2}$ and $2p_{1/2}$ of V^{5+} at 517.7 and 525.2 eV, whereas O 1s peaks appear at 531.1 and 530.5 eV respectively. In addition we observed small nitrogen impurity peaks at 399.9 and 401.9 eV respectively, probably arising from hydrazine hydrate used in the synthesis of 1%Ru@ V_2O_5 .

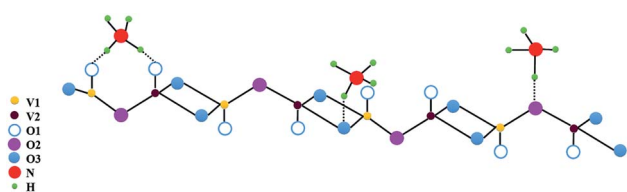


Fig. 11 Adsorption sites for NH_3 adsorption at Brønsted acid sites consisting of singly coordinated, di-coordinated and tri-coordinated oxygen sites on V_2O_5 surface atoms.

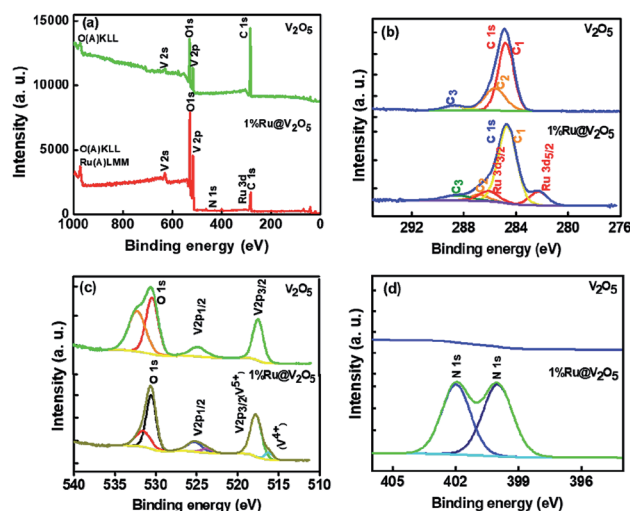



Fig. 12 XPS spectra of V_2O_5 and 1%Ru@ V_2O_5 .



Fig. 13(a) shows bare and 1%Ru@V₂O₅ surfaces. On V₂O₅ as no RuO₂/Ru particles are present, there is no water adsorption and consequently no NH₃ adsorption shown. This results into a situation as depicted in Fig. 13(b) as far as the bands are concerned. When there is no ruthenium oxide on the surface and bare V₂O₅ is exposed to the surface, less charge carriers are produced and resistance of V₂O₅ does not change much. When RuO₂/Ru nanoparticles are present on the V₂O₅ surface they form a semiconductor-semiconductor contact, which in turn forms a depletion layer similar to that on V₂O₅.⁵⁷ Now, unlike on V₂O₅, water molecules dissociate on ruthenium (or oxide) leading to liberation of electrons, which are easily transferred to V₂O₅ reducing the resistance. Thus higher sensitivity of 1% Ru@V₂O₅ compared to bare V₂O₅ is followed. It can be inferred from above discussion that Ru/RuO₂ nanoclusters on the V₂O₅ microcrystallites assist the dissociation of water molecules. This is helpful for V₂O₅ to dissociate NH₃, which in turn liberates free electrons.

(5) Sensor 1%Ru@V₂O₅ is selective, sensitive, has low response and recovery time. Here oxygen defects are not probably playing important role, as such centers would be thermally activated. We obtain more sensitivity at room temperature than at higher temperatures.

- 1 Y. Wu, G. Gao and G. Wu, *J. Mater. Chem. A*, 2015, **3**, 1828.
- 2 Y. T. Wang, W. T. Whang and C. H. Chen, *ACS Appl. Mater. Interfaces*, 2015, **7**, 8480.
- 3 M. Kodu, A. Berholts, T. Kahro, M. Kook, P. Ritslaid, H. Seemen, T. Avarmaa, H. Alles and R. Jaaniso, *Beilstein J. Nanotechnol.*, 2017, **8**, 571.
- 4 K.-Y. Pan and D.-H. Wei, *Nanomaterials*, 2016, **6**, 140.
- 5 C. Bianchi, L. M. Ferreira, J. Loureiro, A. Rodrigues, P. Duarte, A. C. Baptista and I. M. Ferreira, *J. Electron. Mater.*, 2016, **45**, 1987.
- 6 M. A. Centeno, I. Carrizosa and J. A. Odriozola, *Appl. Catal., B*, 2001, **29**, 307.
- 7 J. Livage, Vanadium pentoxide gels, *Chem. Mater.*, 1991, **3**, 578.
- 8 J. Livage, *Materials*, 2010, **3**, 4175.

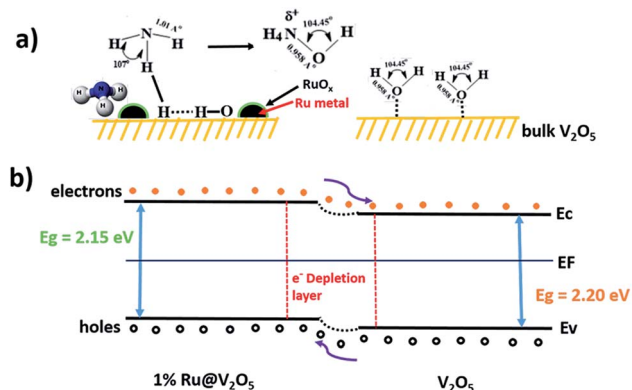

This journal is © The Royal Society of Chemistry 2019

- 9 M. Yu, X. Liu, Y. Wang, Y. Zheng, J. Zhang, M. Li, W. Lan and Q. Su, *Appl. Surf. Sci.*, 2012, **258**, 9554.
- 10 D. Raj, T. Pazhanivel, P. S. Kumar, D. Mangalaraj, D. Nataraj and N. Ponpandian, *Curr. Appl. Phys.*, 2010, **10**, 531.
- 11 M. Wu, X. Zhang, S. Gao, X. Cheng, Z. Rong, Y. Xu, H. Zhao and L. Huo, *CrystEngComm*, 2013, **15**, 10123.
- 12 V. Modafferi, G. Panzera, A. Donato, P. L. Antonucci, C. Cannilla, N. Donato, D. Spadaro and G. Neri, *Sens. Actuators, B*, 2012, **163**, 61.
- 13 W. Jin, S. Yan, L. An, W. Chen, S. Yang, C. Zhao and Y. Dai, *Sens. Actuators, B*, 2015, **206**, 284.
- 14 Y. Qin, G. Fan, K. Liu and M. Hu, *Sens. Actuators, B*, 2014, **190**, 141.
- 15 S. A. Hakim, Y. Liu, G. S. Zakharova and W. Chen, *RSC Adv.*, 2015, **5**, 23489.
- 16 B. J. Liu, X. Wang and Q. Peng, *Materials*, 2005, **17**, 764.
- 17 I. Raible, M. Burghard, U. Schlecht, A. Yasuda and T. Vossmeier, *Sens. Actuators, B*, 2005, **106**, 730.
- 18 M. Hasan, M. O. Ansari, M. H. Cho and M. Lee, *J. Ind. Eng. Chem.*, 2015, **22**, 147.
- 19 J. Huotari, J. Lappalainen, J. Eriksson, R. Bjorklund, E. Heinonen, I. Miinalainen, J. Puustinen and A. Lloyd Spetz, *J. Alloys Compd.*, 2016, **675**, 433.
- 20 J. M. Cocciantelli, P. Gravereau, J. P. Doumerc, M. Pouchard and P. Hagenmuller, *J. Solid State Chem.*, 1991, **93**, 497.
- 21 J. Huotari, V. Kekkonen, J. Puustinen, J. Liimateinen and J. Lappalainen, *Procedia Eng.*, 2016, **168**, 1066.
- 22 J. Huotari, R. Bjorklund, J. Lappalainen and A. Lloyd Spetz, *Sens. Actuators, B*, 2015, **217**, 22.
- 23 W. Jin, S. Yan, W. Chen, S. Yang, C. Zhao and Y. Dai, *Mater. Lett.*, 2014, **128**, 362.
- 24 J. Liang, K. Zhu, R. Yang and M. Hu, *Ceram. Int.*, 2018, **44**, 2261.
- 25 P. Dutta and A. D. Adeyemo, *14th Int. Meet. Chem. Sensors.*, 2012, p. 152.
- 26 J. M. Patil, S. B. Patil, R. H. Bari and A. N. Sonar, *Int. J. Chem. Concepts*, 2016, **2**, 12.
- 27 R. Wang, S. Yang, R. Deng, W. Chen, Y. Liu, H. Zhang and G. S. Zakharova, *RSC Adv.*, 2015, **5**, 41050.
- 28 F. Zhang, X. Wang, J. Dong, N. Qin and J. Xu, *Sens. Actuators, B*, 2013, **186**, 126.
- 29 K. Chebout, A. Iratni, A. Bouremana, K. Mhammedi, H. Menari, A. Keffous and N. Gabouze, *The Third Int. Conf. Sens. Devices & Tech. Appl.*, 2012, ISBN, 978-1-61208-208-042.
- 30 K. Chebout, R. Tala-Ighil, K. Mhammedi, S. Sam and N. Gabouze, *Res. Rev.: J. Eng. Technol.*, 2018, **7**, 24–29, E-ISSN: 2319-9873.
- 31 W. Yan, M. Hu, J. Liang, D. Wang, Y. Wei and Y. Qin, *Nano*, 2016, **7**, 1650079.
- 32 P. V. Adhyapak, A. D. Bang, P. More and N. R. Munirathnam, *RSC Adv.*, 2018, **8**, 34035.
- 33 G. P. Nagabhushana and G. T. Chandrappa, *J. Mater. Chem. A*, 2013, **1**, 11539.
- 34 V. V. Porsev, A. V. Bandura and R. A. Evarestov, *Acta Mater.*, 2014, **75**, 246.
- 35 V. P. Filonenko, M. Sundberg, P. E. Werner and I. P. Zibrov, *Acta Crystallogr., Sect. B: Struct. Sci.*, 2004, **60**, 375.
- 36 N. Pinna, M. Willinger, K. Weiss, J. Urban and R. Schlo, *Nano Lett.*, 2003, **3**, 1131.
- 37 R. A. Elsalamony and S. A. Mahmoud, *Arabian J. Chem.*, 2017, **10**, 194.
- 38 X. Yin, H. Han, I. Gunji, A. Endou, S. S. Cheettu Ammal, M. Kubo and A. Miyamoto, *J. Phys. Chem. B*, 1999, **103**, 4701.
- 39 A. A. Bahgat, F. A. Ibrahim and M. M. El-Desoky, *Thin Solid Films*, 2005, **489**, 68.
- 40 P. Singh and D. Kaur, *J. Appl. Phys.*, 2008, **4**, 103.
- 41 J. Wu, K. Tao, J. M. Miao and L. Norford, *ACS Appl. Mater. Interfaces*, 2015, **7**(49), 27502.
- 42 F. Hoshyargar, M. Shafiei, C. Piloto, N. Motta and P. A. O. Mullane, *J. Mater. Chem. C*, 2016, **4**, 11173.
- 43 S. Cui, J. Wang and X. Wang, *RSC Adv.*, 2015, **5**, 58211.
- 44 V. Khambalkar, S. Birajdar, P. Adhyapak and S. Kulkarni, *Nanotechnology*, 2019, **30**(10), 105501.
- 45 A. Marikutsa, A. Sukhanova, M. Rumyantseva and A. Gaskov, *Sens. Actuators, B*, 2018, **255**(30), 3523.
- 46 H. Fu, X. Yang, X. An, W. Fan, X. Jiang and A. Yu, *Sens. Actuators, B*, 2017, **252**, 103.
- 47 N. Singh, A. Umar, N. Singh, H. Fouad, O. Y. Alothman and F. Z. Haque, *Mater. Res. Bull.*, 2018, **108**, 266.
- 48 V. Modafferi, S. Trocino, A. Donato, G. Panzera and G. Neri, *Thin Solid Films*, 2013, **548**, 689.
- 49 C. Wang, X. Li, Y. Yuan, B. Wang, J. Huang, F. Xia, H. Zhang and J. Xiao, *Sens. Actuators, B*, 2017, **241**, 268.
- 50 M. C. Santos, O. H. C. Hamdan, S. A. Valverde, E. M. Guerra and R. F. Bianchi, *Org. Electron.*, 2018, **65**, 116.
- 51 J. Huotari, R. Bjorklund, J. Lappalainen and A. Spetz, *Procedia Eng.*, 2014, **87**, 1035.
- 52 A. Bielański, J. Piwowarczyk and J. Poźniczek, *J. Catal.*, 1988, **113**, 334.
- 53 D. Sun, Q. Liu, Z. Liu, G. Gui and Z. Huang, *Appl. Catal., B*, 2009, **92**, 462.
- 54 M. Inomata, A. Miyamoto and Y. Murakami, *J. Phys. Chem.*, 1981, **85**, 2372.
- 55 A. Chakrabarti, K. Hermann, R. Druzinic, M. Witko, F. Wagner and M. Petersen, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1999, **59**, 10583.
- 56 A. Marikutsa, V. Krivetskiy, L. Yashina, M. Rumyantseva, E. Konstantinova, A. Ponzoni, E. Comini, A. Abakumov and A. Gaskov, *Sens. Actuators, B*, 2012, **175**, 186.
- 57 J. F. Moulder, E. Stickle, P. E. Sobol and K. D. Bomben, *Handbook of X-ray Photoelectron Spectroscopy*.
- 58 V. Kumar, V. Patil, A. Apte, N. Harale, P. Patil and S. Kulkarni, *Langmuir*, 2015, **31**(48), 13247.
- 59 Y. Wang, H. Shang, T. Chou and G. Cao, *J. Phys. Chem. B*, 2005, **109**(22), 11361.

