

Cite this: *Chem. Sci.*, 2019, **10**, 1823

All publication charges for this article have been paid for by the Royal Society of Chemistry

Received 5th November 2018
Accepted 24th November 2018DOI: 10.1039/c8sc04940h
rsc.li/chemical-science

Introduction

Inspired by the facility of small molecular activation at multi-nuclear enzyme active sites¹ and the enhanced reactivity of high nuclearity defect sites in heterogeneous catalysts,² substantial effort has been directed towards developing multinuclear synthetic catalysts.³ Leveraging the potential opportunities for chemical catalysis that arise from cooperative redox chemistry between transition metal ions (*i.e.* M–M cooperation) requires synthetic access to polynuclear aggregates that feature specific nuclearity and geometry that engender efficient metal–metal (M–M) cooperation.⁴ Extant polynuclear catalysts are accessed by either (1) design and synthesis of multidentate ligands that enforce specific aggregation size and geometry,⁵ or (2) by self-assembly of transition metal ions with simple bridging ligands. These strategies are inherently limiting with respect to the structures that can be evaluated as potential catalysts because (1) the ligands required to stabilize targeted complexes may not be compatible with catalytic applications,⁶ and (2) the self-assembled structures may not give rise to the geometry required for efficient M–M interaction.

In the context of developing new oxidation catalysts, we have become interested in controlling the aggregation state of

transition metal ions in oxidatively resistant ligand scaffolds, such as all-oxygen fields (*i.e.* metal carboxylates). Examination of the self-assembled aggregates of metal carboxylates highlights both the diversity of aggregation sizes and geometries available to simple combinations of metals and ligands, and the challenge inherent in relying on self-assembled aggregates in catalysis. Rh(II) acetate self-assembles as a dimer (*i.e.* Rh₂(OAc)₄) due to the presence of a Rh–Rh bond (Fig. 1a).⁷ The activity of Rh₂(OAc)₄ in carbene group transfer catalysis has been ascribed to M–M cooperation mediated through the M–M bond.⁸ Iso-structural complexes of Group 10 metals are unavailable:

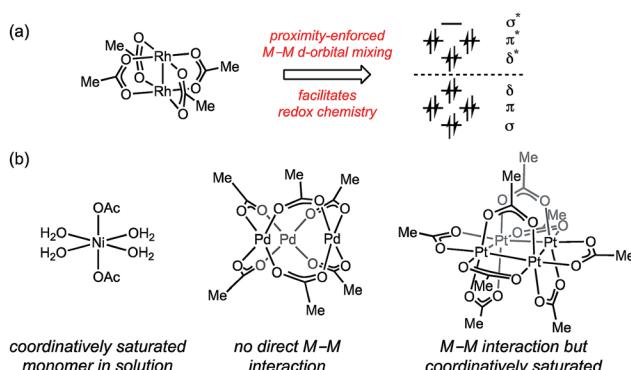


Fig. 1 (a) Rh₂(OAc)₄ features a Rh–Rh single bond, which both enforces formation of a binuclear complex and mediates the redox cooperation between the metal centers responsible for M–M cooperation. (b) Group 10 metal acetates display a range of aggregation sizes and geometries, none of which supports both substrate binding and cooperative redox chemistry.

^aTexas A&M University, Department of Chemistry, College Station, TX 77843, USA.
E-mail: david.powers@chem.tamu.edu

^bDND-CAT, Northwestern Synchrotron Research Centre at the Advanced Photon Source, Argonne, IL 60439, USA

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8sc04940h

$\text{Ni}(\text{OAc})_2$ is a solvated monomer under many conditions,⁹ $\text{Pd}(\text{OAc})_2$ is an acetate-bridged dimer in both solution- and solid-state (*i.e.* $\text{Pd}_3(\text{OAc})_6$),^{10,11} and $\text{Pt}(\text{OAc})_2$ is tetrameric (*i.e.* $\text{Pt}_4(\text{OAc})_8$).^{10a,12–14} The self-assembled, thermodynamically preferred aggregates of these salts do not provide platforms that engender cooperative M–M interactions (Fig. 1b).

Pd_2 intermediates supported by oxygen-rich ligand environments have been proposed in electrochemical methane oxidation,¹⁵ directed C–H oxidation chemistry,¹⁶ and are of interest as models for PdO combustion catalysts.¹⁷ Fig. 2 illustrates the small family of acetate-rich Pd_2 aggregates that have been described. Stahl¹⁸ and Sanford¹⁹ have independently reported that pyridyl donors can support acetate-bridged complexes (**1**–**3**). Acetate-bridged cyclometallated complexes (*i.e.* **4**) have been observed during, and isolated from, directed C–H oxidation reactions.¹⁶ $\text{Pd}_2(\text{OAc})_2(\text{acac})_2$ (**5**) has been obtained by treatment of $\text{Pd}_3(\text{OAc})_5(\text{NO}_2)$ with acetylacetone (*acac* = acetylacetone).²⁰ Related acetate-bridged Pd_2 species supported by γ -Keggin silicocatungstate ligands have been characterized.²¹ In the presence of exogenous acetate ion—conditions relevant to the Wacker-type conversion of ethylene to vinyl acetate—concentration-dependent Pd aggregation has been observed. At intermediate acetate concentration, the dimer $[\text{Pd}_2(\text{OAc})_6]^{2-}$ (**6**) has been characterized by UV-vis and Raman spectroscopies; at high acetate concentrations, $[\text{Pd}(\text{OAc})_4]^{2-}$ speciation has been suggested.²² While $\text{Pd}_2(\text{OAc})_4$ structures that are isostructural to $\text{Rh}_2(\text{OAc})_4$ have been the subject of numerous theoretical investigations,^{19,23} this aggregation mode has not been observed or characterized experimentally.

We are interested in Pd_2 tetracarboxylate sites as potential redox catalysts based on the dual hypotheses that d-orbital mixing will give rise to cooperative redox chemistry in these structures⁴ and that the unavailability of $\text{Pd}_2(\text{OAc})_4$ aggregates has prevented evaluation of the chemistry of this structural motif. Post-synthetic ion metathesis in metal–organic frameworks (MOFs)—a process in which metal sites in a template porous lattice are exchanged with exogenous ions—has been demonstrated to be a method that can enable access to novel coordination geometries.^{24,25} Ion metathesis chemistry has not

been demonstrated for the introduction of 2nd- or 3rd-row transition metals.²⁶ Here, we demonstrate that ion metathesis of binuclear transition metal sites in pre-formed porous crystalline materials provides a targeted strategy to rationally access Pd_2 sites that are metastable in solution-phase chemistry. The new Pd_2 -based lattice is characterized by a combination of powder- (PXRD) and single-crystal X-ray diffraction (SCXRD), X-ray absorption spectroscopy (X-ray absorption near edge structure (XANES) and extended X-ray absorption fine structure (EXAFS)), and gas adsorption analysis. We demonstrate that proximity-enforced Pd – Pd interaction gives rise to cooperative binding of substrates, such as CS_2 , which is not observed for $\text{Pd}_3(\text{OAc})_6$.

Results

Computational evaluation of Pd carboxylate aggregation

We have evaluated the isodesmic aggregation equilibria illustrated in Fig. 3. Geometry optimizations were carried out with B3LYP functional²⁷ with LANL2TZ + f (1.472) basis set and corresponding ECP for Pd ²⁸ and 6-31G(d) basis set for other atoms (coordinates of optimized structures are tabulated in Tables S1–S4†).²⁹ Frequency calculations at this level of theory confirmed that optimized geometries represent ground state structures. Single-point energy calculations were carried out using the M06 functional³⁰ with sdd basis set for Pd ³¹ and the 6-311++G(d,p) basis set for light atoms.³² Single-point solvation energies in acetonitrile were calculated using the SMD solvation model.³³ These methods reproduce available structural data for $\text{Pd}_3(\text{OAc})_6$ and have been demonstrated to provide reliable energies for related Pd carboxylate systems.^{23b} Initial geometries for Pd_2 and Pd_4 aggregates were supplied as Pd substitution of known $\text{Rh}_2(\text{OAc})_4$ and $\text{Pt}_4(\text{OAc})_8$ structures, respectively.^{7,12} The geometry of $\text{Pd}_3(\text{OAc})_6$ was based on its reported X-ray structure.^{10b} Consistent with solid-state and solution-phase measurements, these calculations indicate that trimeric $\text{Pd}_3(\text{OAc})_6$ (Pd – Pd : 3.23 Å) is the thermodynamically preferred aggregate. $\text{Pd}_2(\text{OAc})_4$ (Pd – Pd : 2.62 Å), the next-most stable aggregate, is +5.0 kcal mol^{−1} relative to $\text{Pd}_3(\text{OAc})_6$. The highest occupied molecular orbitals (HOMOs) of $\text{Pd}_2(\text{OAc})_4$ and $\text{Pd}_3(\text{OAc})_6$ are dominated by $4d_{z^2}$ contributions from each of the Pd centers (Fig. 3b and c). The σ^* interaction highlighted in the HOMO of $\text{Pd}_2(\text{OAc})_4$ aggregates are responsible for the relative instability of $\text{Pd}_2(\text{O}_2\text{CR})_4$ sites and alleviation of these interactions drives the observed trimeric structure of Pd carboxylates.

Synthesis of Pd_2 -based materials by ion exchange

We initiated our investigations of ion metathesis to generate metastable Pd_2 aggregates using M_3btc_2 ($\text{btc} = 1,3,5$ -benzenetricarboxylate) networks because (1) these networks feature carboxylate-bridged binuclear sites, (2) a variety of metal ions have been demonstrated to give rise to isostructural networks,³⁴ and (3) we have an ongoing interest in the group-transfer chemistry of M_2 sites housed in this class of materials.³⁵ We specifically identified Zn_3 - and Cu_3btc_2 networks based on the similarity of the ionic radii of Zn , Cu , and Pd within carboxylate

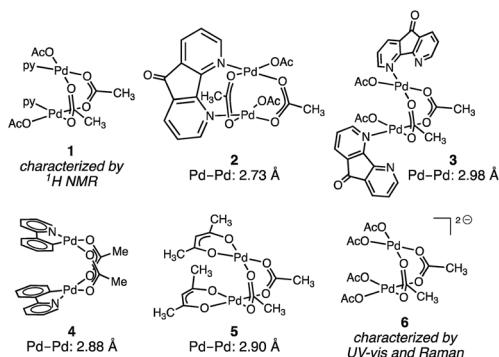


Fig. 2 Available oxygen-rich Pd_2 complexes. The structure of complex **1** was assigned by ^1H NMR spectroscopy. Complexes **2**–**5** have been characterized crystallographically and the structure of $[\text{Pd}_2(\text{OAc})_6]^{2-}$ (**6**) has been proposed based on UV-vis and Raman spectroscopies.



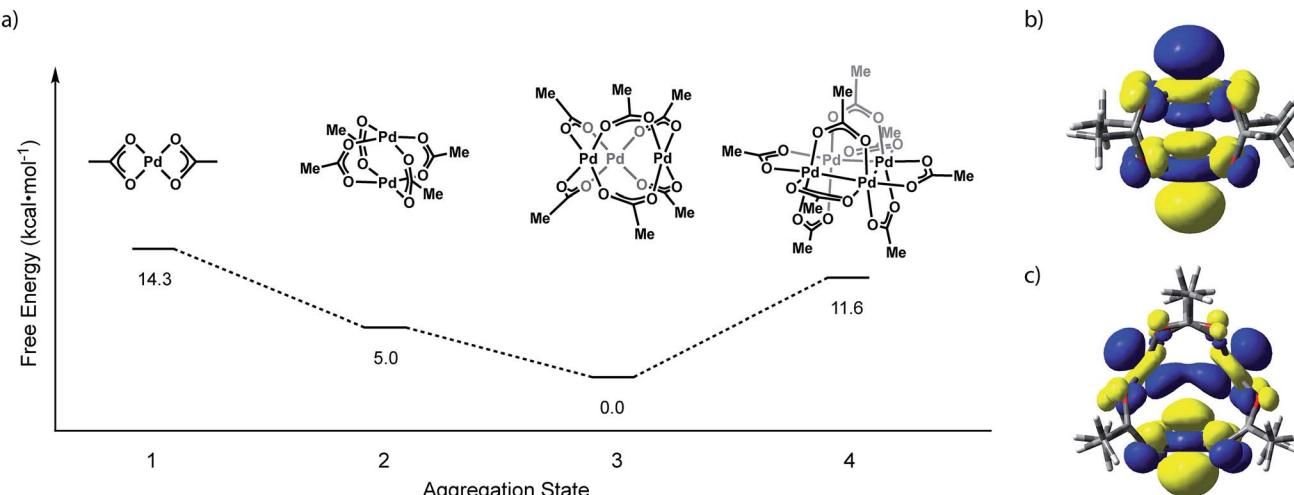


Fig. 3 (a) Plot of free energy versus aggregate size for the aggregation equilibria available to $\text{Pd}(\text{OAc})_2$. Illustrations of the HOMO of (b) $\text{Pd}_2(\text{OAc})_4$ and (c) $\text{Pd}_3(\text{OAc})_6$.

ligand frameworks.³⁶ Molecular heterobimetallic complexes $\text{PdZn}(\text{OAc})_4 \cdot \text{H}_2\text{O}$ and $\text{PdCu}(\text{OAc})_4 \cdot \text{H}_2\text{O}$ are known,³⁷ and the Pd–O distances in these structures are well matched: Pd–O for $\text{PdZn}(\text{OAc})_4 \cdot \text{H}_2\text{O} = 2.007 \text{ \AA}$, Pd–O for $\text{PdCu}(\text{OAc})_4 \cdot \text{H}_2\text{O} = 2.000 \text{ \AA}$, Cu–O = 1.997 \AA , and Zn–O = 2.057 \AA .

Ion metathesis experiments were carried out by soaking pre-formed template lattices in solutions containing Pd(II) sources. The soaking solution was refreshed weekly. The extent of ion exchange was evaluated by inductively coupled plasma-mass spectrometry (ICP-MS) analysis of solutions prepared by exhaustively washing exchanged materials with both the solvent used in the soaking experiment and MeCN followed by digestion of the solid material with aqueous HNO_3 .³⁸ We initiated our experiments by examining potential ion exchange chemistry into Cu_3btc_2 . We examined a variety of Pd sources ($\text{Pd}(\text{OAc})_2$, $\text{Pd}(\text{O}_2\text{CCF}_3)_2$, PdCl_2 , and $[\text{Pd}(\text{CH}_3\text{CN})_4][\text{BF}_4]_2$) in a series of reaction solvents (CHCl_3 , CH_3CN , MeOH, EtOH, and DMF) between 23–80 °C. Under no condition were we able to detect substantial Pd(II) incorporation into the Cu-based network (<1% exchange; these experiments are summarized in Table S5†).³⁶ Based on the demonstration that Zn sites can be fluxional in the Zn_4O nodes of MOF-5,³⁹ we turned our attention to exchange experiments with Zn_3btc_2 . Treatment of Zn_3btc_2 with CHCl_3 solutions of $\text{Pd}_3(\text{OAc})_6$ for 20 d results in ~35% exchange of Zn for Pd. While further soaking with Pd^{2+} solutions did not result in increased Pd incorporation, the partially exchanged material was isomorphous with Zn_3btc_2 (for PXRD, see Fig. S1†) which indicated the viability of Pd exchange into lattice sites of M_2 -based materials. Fig. S1b† compares the PXRD patterns obtained for Zn_3btc and Pd-exchanged btc-based networks with the PXRD pattern that would be following network reorganization accommodate trigonal prismatic nodes (*i.e.* analogous to the structure of $\text{Pd}_3(\text{OAc})_6$), and demonstrates that the extended M_2 -based lattice is not changed upon ion metathesis.

To access materials with greater Pd incorporation, we examined the ion metathesis chemistry of other Zn_2 -based porous materials (data summarized in Tables S6 and S7†). Large families of metal-organic frameworks are available in which

carboxylate linkers support the targeted M_2 coordination sites, and the extent of ion exchange has previously been reported to correlate with linker flexibility.^{25b} Among the Zn-based porous frameworks that were investigated, Zn_3btei (btei = 5,5',5''-(benzene-1,3,5-triyltris(ethyne-2,1-diyl))triisophthalate)⁴⁰ was identified as participating in the most efficient ion metathesis chemistry, affording 79% Pd exchange after 112 d (Fig. 4a, black trace). The Pd-exchanged material is isomorphous to Zn_3btei based on powder X-ray diffraction analysis (Fig. 4b). Soaking the exchanged materials in CHCl_3 for 14 days resulted in no Pd leaching (ICP-MS analysis). Consistent with our observations with Zn_3btc_3 and Cu_3btc_2 , as well as observations of others regarding the relative facility of ion metathesis of Cu and Zn sites,^{25b} exchange into Cu_3btei afforded 20% exchange after 56 d.

Ion metathesis of Pd^{2+} into Zn_3btei is reversible. Exposure of the Pd-exchanged material to CH_3CN solutions of $\text{Zn}(\text{NO}_3)_2$ led to the back exchange to regenerate Zn_3btei (Fig. 4b).

Impact of solvation on ion metathesis

Ion metathesis reactions are often stymied by slow exchange kinetics.^{24c} We were intrigued by the observed (and reproducible) sigmoidal exchange profile pictured in Fig. 4a. Fig. 4a illustrates that exchange is slow for the first ~30 days, after which point substantially more rapid Pd incorporation is observed. The sigmoidal kinetics behavior is not related to sample morphology: two preparations, one using $\text{Zn}(\text{NO}_3)_2$ and the other based on ZnBr_2 , have been reported and afford Zn_3btei as either a microcrystalline powder or as single crystals.⁴⁰ Examination of these two samples resulted in similar exchange *vs.* time plots (Fig. 4a, black *vs.* blue traces).

The IR spectrum of as-synthesized Zn_3btei displays a stretching frequency at 1650 cm^{-1} , which has been assigned as Zn-bound DMF ligands (Fig. S2†).^{36,41} As exchange chemistry is carried out in CHCl_3 , the intensity of this feature diminishes over the course of ~30 days. Thermogravimetric analysis-mass spectrometry (TGA-MS) analysis of samples obtained following



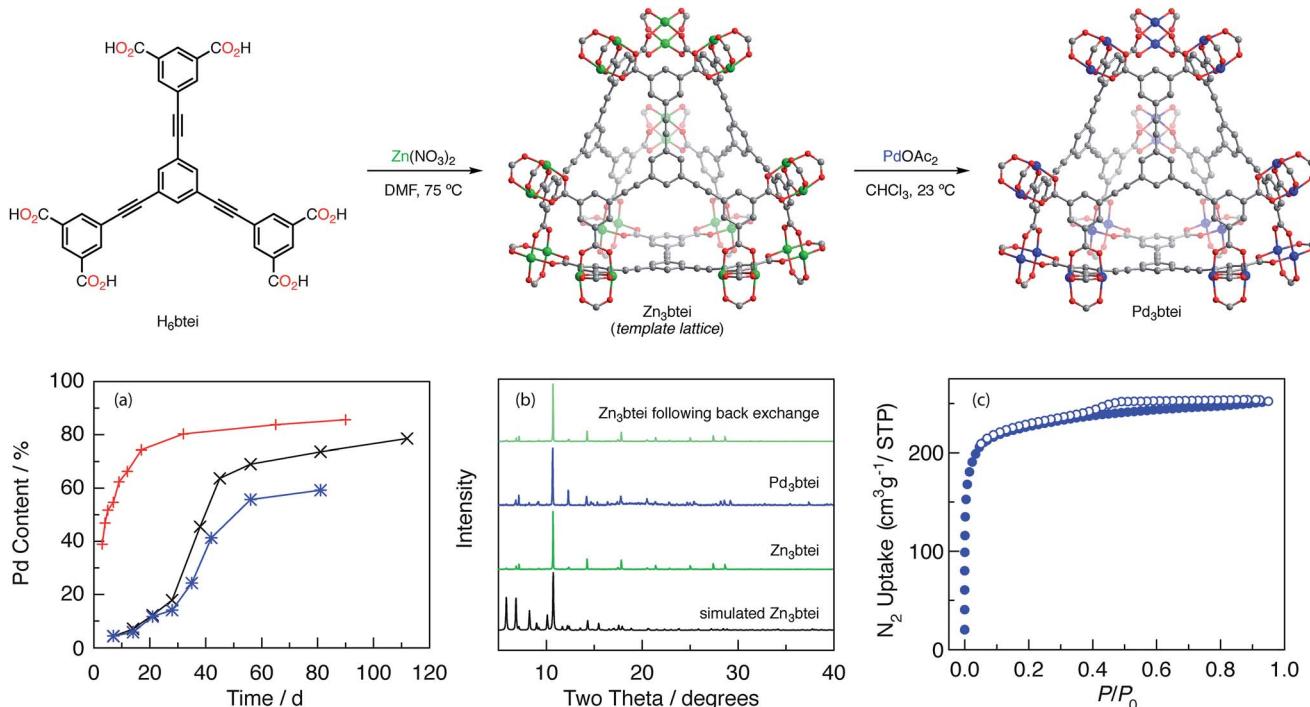


Fig. 4 Synthesis of Zn₃btei and ion exchange with Pd(II) to generate Pd₃btei. (a) Plot of Pd incorporation into Zn₃btei as a function of time. Data plotted for soaking into a microcrystalline powder of Zn₃btei (—), crystalline Zn₃btei (—), and Zn₃btei that was solvent-activated with CHCl₃ (—). (b) From bottom to top: simulated PXRD of Zn₃btei, experimental PXRD of as-synthesized Zn₃btei, experimental PXRD of Pd₃btei, and PXRD of Zn₃btei obtained by back exchange of Pd₃btei with Zn(II). (c) N₂ adsorption isotherm of Pd₃btei (adsorption (●), desorption (○)) obtained at 77 K.

exposure to CHCl₃ for varying lengths of time confirms that concurrent with the disappearance of the carbonyl stretching mode from the IR spectrum, DMF solvent is removed from the Zn material; after 27 days of soaking, DMF is no longer observed (Fig. S3†). Similar activation of metal sites by chlorinated solvents has been observed by treating DMF-solvated Cu₃btc₂ with CH₂Cl₂.⁴²

We hypothesized that the DMF ligated Zn sites that are present in as-synthesized Zn₃btei participate in exchange more slowly than sites with weak donors, such as CHCl₃, that are generated by solvent activation of Zn₃btei. To interrogate this hypothesis, we soaked a sample of Zn₃btei in CHCl₃ for 30 days, after which time we exposed the solvent-activated sample to Pd(II) sources (Fig. 4a, red trace). In this exchange reaction, no induction period for Zn-to-Pd exchange is observed and 86% Pd incorporation is achieved after 90 days (Fig. S4a†). Using solvent-exchanged materials, the rate of Pd incorporation is dependent on the Pd salt used for exchange. For example, ion exchange with Pd(NO₃)₂ is much faster than with Pd(OAc)₂ (88% incorporation is observed after 10 days, Fig. S4b†). The faster uptake is associated with a loss of material crystallinity (Fig. S4c†) so in subsequent experiments we have utilized Pd₃btei prepared from exchange with Pd(OAc)₂.

Gas adsorption

Zn₃btei has been reported to be a non-porous material, which has been attributed to network collapse upon desolvation;⁴⁰ see Fig. S5† for gas adsorption analysis of Zn₃btei. The N₂-adsorption isotherm obtained for a sample of Pd₃btei activated under

the same conditions used for Zn₃btei (evacuation at 23 °C, see Fig. S5† for other activation protocols) provided a BET surface area of 857 m² g⁻¹ (a Langmuir surface area of 991 m² g⁻¹; Fig. 4c). While substantially higher than the surface area measured for Zn₃btei, the BET surface area of Pd₃btei is less than that of the isostructural Cu₃btei material (reported BET surface area of 3730 m² g⁻¹,^{40a} theoretical surface area is 3677 m² g⁻¹, see ESI† for the details of calculation).

Single-crystal X-ray diffraction

Zn₃btei (rht-topology) crystallizes in the *Fm*̄*m* space group and the asymmetric unit contains two Zn ions.⁴⁰ We have examined a single crystal that was isolated following partial Pd exchange (the Pd content of the sample from which the crystal was isolated was 49% (ICP-MS); crystallography details are compiled in Table S8†). Refinement of metal site occupancy in this partially exchanged crystal indicated exchange of one of the symmetry inequivalent Zn sites: Zn(1) has not undergone any exchange while Zn(2) has been ~40% exchanged. Concurrent with exchange, the occupancy of the apical ligand associated with the site undergoing exchange decreases. This observation is consistent with five-coordinate Zn(II) ions being replaced by four-coordinate, square planar Pd(II) ions. While PXRD measurements of fully exchanged Pd₃btei indicated that bulk crystallinity is maintained during exchange, single crystallinity was not maintained during complete exchange, which prevented acquisition of SCXRD data for fully exchanged btei networks.



X-ray absorption spectroscopy

Extended X-ray absorption fine structure (EXAFS) analysis was pursued to interrogate the coordination environment of the metal sites during and after ion exchange. We have analyzed Zn_3btei , Pd_3btei , as well as partially exchanged sample ($\sim 50\%$ exchange). In addition, we have examined $\text{PdZn}(\text{OAc})_4 \cdot \text{H}_2\text{O}$ as a molecular model of partially exchange heterobimetallic Pd-Zn sites. Data and fitting parameters are collected in Fig. S6–S10 and Tables S9–S13[†] and M–M distances obtained from these data sets are tabulated in Table 1.

The Zn K-edge data obtained for Zn_3btei indicate that the coordination environment about Zn is comprised of four Zn–O distances at 2.00 Å, one Zn–O distance at 2.17 Å, and a Zn–Zn distance of 2.86 Å, which is consistent with the known pentacoordinate Zn environment in solvated Zn_3btei .

EXAFS data collected following partial Pd exchange were fit as a mixture of Zn_2 , PdZn , and Pd_2 sites (1 : 2 : 1 ratio). The Zn K-edge data indicated the Zn coordination environment in partially exchanged samples displays four Zn–O distances at 2.01 Å and one Zn–O distance at 2.18 Å. The Zn_2 sites display a Zn–Zn distance of 2.90 Å and the PdZn sites display a Pd–Zn separation of 2.60 Å. The Pd K-edge data collected for the same sample were fit with four Pd–O distances of 2.01 Å. The PdZn sites display a Pd–Zn separation of 2.65 Å and the Pd_2 sites show a Pd–Pd distance of 2.70 Å. The Pd–Zn distance determined from this sample is consistent with the Pd–Zn separation in the molecular site mimic $\text{PdZn}(\text{OAc})_4 \cdot \text{H}_2\text{O}$ (2.576 Å (SCXRD), 2.61 Å (EXAFS)).³⁷

The Pd K-edge data obtained for Pd_3btei indicated the coordination environment of Pd is comprised of four Pd–O distances at 1.98 Å and one Pd–Pd distance at 2.72 Å. The obtained EXAFS data set is dominated by Pd–Pd scattering and the best fit does not incorporate a Pd–Zn interaction.

Analysis of the X-ray absorption near edge structure (XANES) data for both partially and completely exchanged samples indicate that Pd is incorporated into the M_3btei network in the +II oxidation state (Fig. S11[†]).⁴³ Based on comparison of the edge energy for $\text{Pd}_3(\text{OAc})_6$, Pd_3btei , $\text{PdZn}(\text{OAc})_4$, and Pd metal, the edge energy is inconsistent with the presence of Pd(0) in the exchanged samples.

Reactivity of lattice-confined Pd_2 sites

We examined the hypothesis that proximity-enforced Pd–Pd interaction would raise the HOMO and result in a more

Table 1 Summary of M–M separations determined by EXAFS

Material	Zn–Zn (Å)	Pd–Zn (Å)	Pd–Pd (Å)
Zn_3btei	2.86	—	—
$\text{Zn}_{1.5}\text{Pd}_{1.5}\text{btei}$	2.90	2.60 ^a ; 2.65 ^b	2.70
Pd_3btei	—	—	2.72
$\text{PdZn}(\text{OAc})_4 \cdot \text{H}_2\text{O}$	—	2.576	—

^a Distance obtained from Zn K-edge data. ^b Distance obtained from Pd K-edge data.

nucleophilic and more easily oxidized Pd site in comparison to Pd carboxylates in which such Pd–Pd proximity is not enforced (*i.e.* the trinuclear structure of $\text{Pd}_3(\text{OAc})_6$). To evaluate this hypothesis we examined the interaction of Pd_3btei with CS_2 . Electron donation into CS_2 is expected to manifest as a weakening of the C–S π -bonds and a low-energy shift in the associated IR stretching frequency.⁴⁴ The IR spectrum of CS_2 -impregnated Pd_3btei displays an 11 cm^{−1} red shift in the IR stretching frequency (Fig. S12[†]). No similar changes were observed upon CS_2 update in Zn_3btei or upon treatment of $\text{Pd}_3(\text{OAc})_6$ with CS_2 .

We have evaluated the reactivity of Pd_3btei towards a variety of reaction conditions. The Pd–O linkages in Pd_3btei are susceptible to protonation: treatment of Pd_3btei with weak acids such as AcOH leads to the digestion of the extended lattice and the evolution of free H_6btei and soluble Pd salts. The proteolytic instability of the Pd–O bonds in Pd_3btei can give rise to reaction chemistry with protic substrates: treatment of Pd_3btei with benzyl alcohol resulted in the evolution of benzaldehyde with the concurrent formation of Pd(0). This observation is consistent with protonation of the Pd–O bond followed by β -hydride elimination of the incipient Pd(II) alkoxide. We have also carried out a series of experiments in which Pd_3btei was treated with oxidants, such as peracetic acid and 2-*tert*-butylsulfonyl iodosylbenzene. Despite attempts to introduce exogenous substrates that might participate in C–H functionalization of olefin oxidation, in all conditions examined, the exclusive oxidation product obtained is 1,3,5-benzene tricarboxylic acid, which is the product of oxidative cleavage of the alkynyl groups in btei ligand. Similar treatment of H_6btei and Zn_3btei also generates 1,3,5-benzene tricarboxylic acid.

Discussion

$\text{Pd}(\text{OAc})_2$ is a ubiquitous catalyst and precatalyst in organic synthesis, and as such the structure of this important molecule has been the focus of sustained interest. Single-crystal X-ray diffraction, EXAFS, and solid-state NMR experiments have confirmed that $\text{Pd}(\text{OAc})_2$ exhibits a trimeric structure (*i.e.* $\text{Pd}_3(\text{OAc})_6$) in the solid state (Fig. 1).^{10b,c} A combination of NMR, Raman, and IR spectroscopies as well as EXAFS data and ebulliometry measurements indicate that the trimeric structure is maintained upon dissolution in many common solvents.^{10a,c–e} Trinuclear aggregation simultaneously satisfies the proclivity for square planar coordination about Pd(II) ions and minimizes overlap of filled 4d₂ orbitals (Fig. 3).

The close Pd–Pd interactions in acetate-bridged binuclear Pd complexes, such as complex 4 (Fig. 2), are credited for Pd–Pd cooperation and facile redox events in some Pd-catalyzed C–H oxidation chemistry.¹⁶ *A priori*, one might expect that attractive d⁸–d⁸ interactions, which arise from symmetry allowed mixing of the 4d orbitals with the 5s and 5p orbitals, could stabilize Pd_2 aggregate.⁴⁵ However, in comparison to Rh, Ir, and Pt, for which attractive d⁸–d⁸ interactions have been documented, Pd exhibits an anomalously large energy gap between the 4d and 5s and 5p orbitals, which attenuates the impact of symmetry-allowed orbital mixing.⁴³ The potential stabilization of mixing



of the 4d with 5p and 5s orbitals is more than compensated for by the enforced filled–filled 4d_{z²} interactions in Pd₂ aggregates. The kinetic instability of Pd₂ aggregation can be overcome with strong donor ligands such as formamidinate and guanidinate ligands,⁴⁶ but the use of such basic ligands can introduce potential ligand-based redox chemistry.⁶ With interest in oxidation catalysis, we have been attracted to identifying strategies to stabilize Pd₂ aggregates in the absence of strongly basic nitrogen donors and have focused on the potential to isolate these structures in oxidation-resistant oxygen ligand fields.

Here, we demonstrate that ion metathesis of Pd(II) into pre-formed Zn(II)-based porous materials enables the synthesis and stabilization of thermodynamically metastable Pd₂ tetracarboxylate sites confined with a porous lattice (Fig. 4). Extended exposure of Zn₂-based materials to Pd(II)-containing solutions results in the replacement of lattice Zn(II) with Pd(II). Based on a combination of SCXRD and EXAFS analysis, the templated Pd₂ sites are installed by sequential replacement of the Zn ions in the template lattice. Pd exchange efficiency depends on both the templating metal ion—Pd exchange is more efficient in Zn₂-based materials than those comprised of Cu₂ sites—and the structure of the organic linkers—Pd exchange into Zn₃btc₂ proceeds only to ~35% Pd incorporation while use of the larger linking group btei enabled exchange reactions to proceed to ~80% Pd incorporation. This observation is consistent with previous reports that larger, potentially more flexible organic linkers, support greater ion metathesis chemistry, which may be due to the ability of these more flexible structures to accommodate the subtle structural differences between materials before and after ion metathesis chemistry.^{25b}

Cation exchange in porous materials has begun to emerge as a powerful strategy to access materials that are unavailable from solvothermal synthetic methods. Based on XANES analysis, the generated Pd₂-based materials are comprised of Pd(II) ions, and the isolated materials do not contain Pd(0). This observation is in contrast to previous solvothermal approaches to Pd₂-containing materials, which result in formation of Pd(0) nanoparticles intercalated within the MOF structure.⁴⁷ These observations highlight the importance of low-temperature cation exchange to generate Pd-based MOFs: facile reduction of Pd(II) at high temperature and in the presence of many of the coordinating solvents typically employed in solvothermal synthesis of porous materials mandates that low-temperature synthetic methods to be developed to introduce Pd(II) sites.

While cation exchange chemistry is an important approach towards designer porous materials, often, the lack of mechanistic information regarding ion metathesis chemistry prevents predictive application of cation exchange reactions to target porous structures. Analysis of the time-dependent reaction progress of Pd exchange into Zn sites has revealed the presence of a kinetic induction period for ion exchange when DMF-solvated Zn templates were employed. At early reaction times, exchange proceeds slowly. At later times, substantially faster exchange is observed (Fig. 4a). IR spectroscopy and TGA-MS experiments, carried out during the kinetic induction period indicated that during this reaction regime, Zn-bound DMF ligands were being removed. The more rapid exchange

chemistry was observed once DMF ligands were completely removed. The importance of network solvation was confirmed by pre-soaking materials in CHCl₃. Ion exchange on these pre-activated materials resulted in ion exchange with no induction period. We hypothesize that the observed solvation-dependent exchange chemistry reflects the increased Lewis acidity of under-ligated Zn(II) ions and the increased proclivity of these ions to bind incoming carboxylate ions delivered by Pd₃(OAc)₆.

The unique electronic structure of the Pd₂ site that is conferred by proximity-enforced Pd–Pd interaction is evidenced by the observation of CS₂ binding. The HOMO-energy-raising impact of d_{z²} mixing provides enhanced Lewis basicity and thus binding of Lewis acidic substrates which is not observed in either Zn₃btei or Pd₃(OAc)₆. Oxidative lability of the alkynyl linkers in the btei ligands has thus far precluded examination of the impact of HOMO-raising on oxidation catalysis with lattice-confined substrates.

Conclusions

The scope of polynuclear complexes that can be evaluated as potential catalyst platforms would be greatly expanded if general strategies to control the size and geometry of discrete aggregates supported by simple ligands were available. Here, we have demonstrated that cation metathesis within porous MOFs can be leveraged to prepare and stabilize Pd₂ tetracarboxylate sites that are metastable in solution-phase chemistry. These studies have revealed the important role that lattice solvation can exert on the course of ion metathesis chemistry. We anticipate that the development of predictive models for when cation exchange chemistry will be facile in combination with access to new templated polynuclear aggregates housed in oxidatively stable ligand environments will contribute to the development of new families of polynuclear catalysts.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We thank Texas A&M University, the Welch Foundation (A-1907), and the U.S. Department of Energy (DE-SC0018977) for financial support. Portions of this work were performed at the DuPont-Northwestern-Dow Collaborative Access Team (DND-CAT) located at Sector 5 of the Advanced Photon Source (APS). DND-CAT is supported by Northwestern University, E.I. DuPont de Nemours & Co., and The Dow Chemical Company. This research used resources of the Advanced Photon Source, a U.S. Department of Energy (DOE) Office of Science User Facility operated for the DOE Office of Science by Argonne National Laboratory under Contract No. DE-AC02-06CH11357. We thank Yu-Sheng Chen for acquisition of sing-crystal X-ray diffraction. NSF's ChemMatCARS Sector 15 is principally supported by the Divisions of Chemistry (CHE) and Materials Research (DMR), National Science Foundation, under grant number NSF/CHE-



1346572. Use of the Advanced Photon Source, an Office of Science User Facility operated for the U.S. Department of Energy (DOE) Office of Science by Argonne National Laboratory, was supported by the U.S. DOE under Contract No. DE-AC02-06CH11357.

References

- (a) R. H. Holm, P. Kennepohl and E. I. Solomon, *Chem. Rev.*, 1996, **96**, 2239; (b) J. P. McEvoy and G. W. Brudvig, *Chem. Rev.*, 2006, **106**, 4455; (c) J. C. Fontecilla-Camps, A. Volbeda, C. Cavazza and Y. Nicolet, *Chem. Rev.*, 2007, **107**, 4273; (d) B. M. Hoffman, D. Lukoyanov, Z.-Y. Yang, D. R. Dean and L. C. Seefeldt, *Chem. Rev.*, 2014, **114**, 4041.
- (a) T. Zambelli, J. Winterlin, J. Trost and G. Ertl, *Science*, 1996, **273**, 1688; (b) R. Schlögl, *Angew. Chem., Int. Ed.*, 2015, **54**, 3465.
- For recent reviews, see: (a) J. P. Krogman and C. M. Thomas, *Chem. Commun.*, 2014, **50**, 5115; (b) K. P. Kornecki, J. F. Berry, D. C. Powers and T. Ritter, *Prog. Inorg. Chem.*, 2014, **58**, 223; (c) I. G. Powers and C. Uyeda, *ACS Catal.*, 2017, **7**, 936; (d) D. R. Pye and N. P. Mankad, *Chem. Sci.*, 2017, **8**, 1705; (e) J. F. Berry and C. M. Thomas, *Dalton Trans.*, 2017, **46**, 5472; (f) N. P. Mankad, *Chem. Commun.*, 2018, **54**, 1291.
- D. C. Powers and T. Ritter, *Acc. Chem. Res.*, 2012, **45**, 840.
- For examples, see: (a) A. Velian, S. Lin, A. J. M. Miller, M. W. Day and T. Agapie, *J. Am. Chem. Soc.*, 2010, **132**, 6296; (b) T. M. Powers, A. R. Fout, S.-L. Zheng and T. A. Betley, *J. Am. Chem. Soc.*, 2011, **133**, 3336; (c) P. A. Rudd, S. S. Liu, N. Planas, E. Bill, L. Gagliardi and C. C. Lu, *Angew. Chem., Int. Ed.*, 2013, **52**, 4449; (d) S. Kuppuswamy, T. M. Powers, J. P. Krogman, M. W. Bezpalko, B. M. Foxman and C. M. Thomas, *Chem. Sci.*, 2013, **4**, 3557; (e) S. E. Flowers and B. M. Cossairt, *Organometallics*, 2014, **33**, 4341; (f) Y. Lee, K. J. Anderton, F. T. Sloane, D. M. Ermert, K. A. Abboud, R. Garcia-Serres and L. J. Murray, *J. Am. Chem. Soc.*, 2015, **137**, 10610.
- For example, N–N coupling has been observed following oxidation in guanidinate-supported complexes: J. B. Diccianni, C. Hu and T. Diao, *Angew. Chem., Int. Ed.*, 2016, **55**, 7534.
- (a) M. A. Porai-Koshits and A. S. Antschishkina, *Dokl. Chem.*, 1962, **146**, 920; (b) F. A. Cotton, B. G. DeBoer, M. D. LaPrade, J. R. Pipal and D. A. Ucko, *J. Am. Chem. Soc.*, 1970, **92**, 2926.
- E. Nakamura, N. Yoshikai and M. Yamanaka, *J. Am. Chem. Soc.*, 2002, **124**, 7181.
- (a) J. N. van Niekirk and F. R. L. Schoening, *Acta Crystallogr.*, 1953, **6**, 609; (b) T. C. Downie, W. Harrison, E. S. Raper and M. A. Hepworth, *Acta Crystallogr., Sect. B: Struct. Crystallogr. Cryst. Chem.*, 1971, **27**, 706.
- (a) T. A. Stephenson, S. M. Morehouse, A. R. Powell, J. P. Heffer and G. Wilkinson, *J. Chem. Soc.*, 1965, 3632; (b) A. C. Skapski and M. L. Smart, *J. Chem. Soc. D*, 1970, 658; (c) V. I. Bakhmutov, J. F. Berry, F. A. Cotton, S. Ibragimov and C. A. Murillo, *Dalton Trans.*, 2005, 1989; (d) V. M. Nosova, Y. A. Ustynyuk, L. G. Bruk, O. N. Temkin, A. V. Kisin and P. A. Storozhenko, *Inorg. Chem.*, 2011, **50**, 9300; (e) L. A. Adrio, B. N. Nguyen, G. Guilera, A. G. Livingston and K. K. Hii, *Catal. Sci. Technol.*, 2012, **2**, 316; (f) W. A. Carole, J. Bradley, M. Sarwar and T. J. Colacot, *Org. Lett.*, 2015, **17**, 5472; (g) R. J. Pakula, M. Srebro-Hooper, C. G. Fry, H. J. Reich, J. Autschbach and J. F. Berry, *Inorg. Chem.*, 2018, **57**, 8046.
- A polymeric crystal structure has also been reported, but this structure has not been widely studied: S. D. Kirik, R. F. Mulagaleev and A. I. Blokhin, *Acta Crystallogr., Sect. C: Cryst. Struct. Commun.*, 2004, **60**, M449.
- M. A. A. F. d. C. T. Carrondo and A. C. Skapski, *Acta Crystallogr., Sect. B: Struct. Crystallogr. Cryst. Chem.*, 1978, **34**, 1857.
- In contrast to tetrameric Pt(II) acetate complexes, dimeric Pt(III) acetate complexes have been observed: T. G. Appleton, K. A. Byriel, J. M. Garrett, J. R. Hall, C. H. L. Kennard, M. T. Mathieson and R. Stranger, *Inorg. Chem.*, 1995, **34**, 5646.
- Oxygen-rich d⁸–d⁸ Pt dimers have been investigated: T. V. Darnton, B. M. Hunter, M. G. Hill, S. Zális, A. Vleek Jr and H. B. Gray, *J. Am. Chem. Soc.*, 2016, **138**, 5699.
- M. E. O'Reilly, R. S. Kim, S. Oh and Y. Surendranath, *ACS Cent. Sci.*, 2017, **3**, 1174.
- (a) D. C. Powers and T. Ritter, *Nat. Chem.*, 2009, **1**, 302; (b) D. C. Powers, M. A. L. Geibel, J. E. M. N. Klein and T. Ritter, *J. Am. Chem. Soc.*, 2009, **131**, 17050; (c) N. R. Deprez and M. S. Sanford, *J. Am. Chem. Soc.*, 2009, **131**, 11234; (d) D. C. Powers, D. Y. Xiao, M. A. L. Geibel and T. Ritter, *J. Am. Chem. Soc.*, 2010, **132**, 14530; (e) D. C. Powers, E. Lee, A. AriaFard, M. S. Sanford, B. F. Yates, A. J. Carty and T. Ritter, *J. Am. Chem. Soc.*, 2012, **134**, 12002; (f) A. J. Carty, A. AriaFard, M. S. Sanford and B. F. Yates, *Organometallics*, 2013, **32**, 544.
- (a) R. Yamauchi, A. Endou, M. Kubo and A. Miyamoto, *Int. J. Quantum Chem.*, 1997, **61**, 673; (b) S. M. Lang, T. Schnabel and T. M. Bernhardt, *Phys. Chem. Chem. Phys.*, 2012, **14**, 9364; (c) S. M. Lang, A. Frank and T. M. Bernhardt, *J. Phys. Chem. C*, 2013, **117**, 9791.
- P. B. White, J. N. Jaworski, C. G. Fry, B. S. Dolinar, I. A. Guzei and S. S. Stahl, *J. Am. Chem. Soc.*, 2016, **138**, 4869.
- A. K. Cook and M. S. Sanford, *J. Am. Chem. Soc.*, 2015, **137**, 3109.
- S. P. Khranenko, E. A. Shusharina and S. A. Gromilov, *J. Struct. Chem.*, 2011, **52**, 544.
- T. Hirano, K. Uehara, K. Kamata and N. Mizuno, *J. Am. Chem. Soc.*, 2012, **134**, 6425.
- (a) R. N. Pandey and P. M. Henry, *Can. J. Chem.*, 1974, **52**, 1241; (b) D. D. Kragten and R. A. van Santen, *Inorg. Chem.*, 1999, **38**, 331.
- (a) D. D. Kragten, R. A. van Santen, M. Neurock and J. J. Lerou, *J. Phys. Chem. A*, 1999, **103**, 2756; (b) Y. F. Yang, G.-J. Cheng, P. Liu, D. Leow, T.-Y. Sun, P. Chen, X. Zhang, J.-Q. Yu, Y.-D. Wu and K. N. Houk, *J. Am. Chem. Soc.*, 2014, **136**, 344; (c) B. E. Haines, H. Xu, P. Verma, X.-C. Wang, J.-Q. Yu and D. G. Musaev, *J. Am. Chem. Soc.*, 2015, **137**, 9022; (d) B. E. Haines, J. F. Berry, J.-Q. Yu and D. G. Musaev, *ACS Catal.*, 2016, **6**, 829.



24 For examples of post-synthetic metal-ion exchange, see: (a) M. Dincă and J. R. Long, *J. Am. Chem. Soc.*, 2007, **129**, 11172; (b) L. Mi, H. Hou, Z. Song, H. Han, H. Xu, Y. Fan and S.-W. Ng, *Cryst. Growth Des.*, 2007, **7**, 2553; (c) C. K. Brozek and M. Dincă, *J. Am. Chem. Soc.*, 2013, **135**, 12886; (d) E. D. Metzger, C. K. Brozek, R. J. Comito and M. Dincă, *ACS Cent. Sci.*, 2016, **2**, 148; (e) L. Liu, L. Li, J. A. DeGayner, P. Winegar, Y. Fang and T. D. Harris, *J. Am. Chem. Soc.*, 2018, **140**, 11444.

25 For relevant reviews: (a) M. Lalonde, W. Bury, O. Karagiardi, Z. Brown, J. T. Hupp and O. K. Farha, *J. Mater. Chem. A*, 2013, **1**, 5453; (b) C. K. Brozek and M. Dincă, *Chem. Soc. Rev.*, 2014, **43**, 5456; (c) P. Dera, J. E. Mondloch, O. Karagiardi, W. Bury, J. T. Hupp and O. K. Farha, *Chem. Soc. Rev.*, 2014, **43**, 5896; (d) M. Bosch, S. Yuan, W. Rutledge and H.-C. Zhou, *Acc. Chem. Res.*, 2017, **50**, 857; (e) S. M. Cohen, *J. Am. Chem. Soc.*, 2017, **139**, 2855.

26 There are a limited number of examples of d^0 and d^{10} ions in the second and third row that have been demonstrated to participate in ion metathesis chemistry. For Hf(IV): M. Kim, J. F. Cahill, H. Fei, K. A. Prather and S. M. Cohen, *J. Am. Chem. Soc.*, 2012, **134**, 18082. For Cd(II): (a) S. Das, H. Kim and K. Kim, *J. Am. Chem. Soc.*, 2009, **131**, 3814; (b) S. Huang, X. Li, X. Shi, H. Hou and Y. Fan, *J. Mater. Chem.*, 2010, **20**, 5695; (c) G. Mukherjee and K. Biradha, *Chem. Commun.*, 2012, **48**, 4293.

27 (a) C. Lee, W. Yang and R. G. Parr, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1988, **37**, 785; (b) A. D. Becke, *J. Chem. Phys.*, 1993, **98**, 1372; (c) A. D. Becke, *J. Chem. Phys.*, 1993, **98**, 5648; (d) P. J. Stephens, F. J. Devlin, C. F. Chabalowski and M. J. Frisch, *J. Phys. Chem.*, 1994, **98**, 1623.

28 (a) P. J. Hay and W. R. Wadt, *J. Chem. Phys.*, 1985, **82**, 299; (b) A. W. Ehlers, M. Böhme, S. Dapprich, A. Gobbi, A. Höllwarth, V. Jonas, K. F. Köhler, R. Stegmann, A. Veldkamp and G. Frenking, *Chem. Phys. Lett.*, 1993, **208**, 111; (c) L. E. Roy, P. J. Hay and R. L. Martin, *J. Chem. Theory Comput.*, 2008, **4**, 1029.

29 (a) R. Ditchfield, W. J. Hehre and J. A. Pople, *J. Chem. Phys.*, 1971, **54**, 724; (b) W. J. Hehre, R. Ditchfield and J. A. Pople, *J. Chem. Phys.*, 1971, **54**, 2257; (c) P. C. Hariharan and J. A. Pople, *Theor. Chim. Acta*, 1973, **28**, 213.

30 Y. Zhao and D. G. Truhlar, *Theor. Chem. Acc.*, 2008, **120**, 215.

31 (a) M. Dolg, U. Wedig, H. Stoll and H. Preuss, *J. Chem. Phys.*, 1987, **86**, 866; (b) D. Andrae, U. Haußermann, M. Dolg, H. Stoll and H. Preuß, *Theor. Chem. Acc.*, 1990, **77**, 123.

32 R. Krishnan, J. S. Binkley, R. Seeger and J. A. Pople, *J. Chem. Phys.*, 1980, **72**, 650.

33 A. V. Marenich, C. J. Cramer and D. G. Truhlar, *J. Phys. Chem. B*, 2009, **113**, 6378.

34 C. R. Wade and M. Dincă, *Dalton Trans.*, 2012, **41**, 7931.

35 (a) A. Das, J. H. Reibenspies, Y.-S. Chen and D. C. Powers, *J. Am. Chem. Soc.*, 2017, **139**, 2912; (b) C.-H. Wang, A. Das, W.-Y. Gao and D. C. Powers, *Angew. Chem., Int. Ed.*, 2018, **57**, 3676.

36 (a) S. S.-Y. Chui, S. M.-F. Lo, J. P. H. Charmant, A. G. Orpen and I. D. Williams, *Science*, 1999, **283**, 1148; (b) X. Song, S. Jeong, D. Kim and M. S. Lah, *CrystEngComm*, 2012, **14**, 5753.

37 N. S. Akhmadullina, N. V. Cherkashina, N. Y. Kozitsyna, I. P. Stolarov, E. V. Perova, A. E. Gekhman, S. E. Nefedov, M. N. Vargaftik and I. I. Moiseev, *Inorg. Chim. Acta*, 2009, **362**, 1943.

38 Experiments in which substantial Pd(0) formation was observed, either visually or by the diagnostic PXRD signal at $\sim 40^\circ$ were not included.

39 C. K. Brozek, V. K. Michaelis, T.-C. Ong, L. Bellarosa, N. López, R. G. Griffin and M. Dincă, *ACS Cent. Sci.*, 2015, **1**, 252.

40 (a) S. Hong, M. Oh, M. Park, J. W. Yoon, J.-S. Chang and M. S. Lah, *Chem. Commun.*, 2009, 5397; (b) D. Zhao, D. Yuan, D. Sun and H.-C. Zhou, *J. Am. Chem. Soc.*, 2009, **131**, 9186.

41 I. Boldog, K. V. Domasevitch, J. Sanchiz, P. Mayer and C. Janiak, *Dalton Trans.*, 2014, **43**, 12590.

42 H. K. Kim, W. S. Yun, M.-B. Kim, J. Y. Kim, Y.-S. Bae, J. Lee and N. C. Jeong, *J. Am. Chem. Soc.*, 2015, **137**, 10009.

43 K.-I. Shimizu, Y. Kamiya, K. Osaki, H. Yoshida and A. Satsuma, *Catal. Sci. Technol.*, 2012, **2**, 767.

44 A. Sahibed-Dine, A. Aboulayt, M. Bensitel, A. B. Mohammed Saad, M. Daturi and J. C. Lavally, *J. Mol. Catal. A: Chem.*, 2000, **162**, 125.

45 J. E. Bercaw, A. C. Durrell, H. B. Gray, J. C. Green, N. Hazari, J. A. Labinger and J. R. Winkler, *Inorg. Chem.*, 2010, **49**, 1801.

46 J. F. Berry, F. A. Cotton, S. A. Ibragimov, C. A. Murillo and X. Wang, *Inorg. Chem.*, 2005, **44**, 6129.

47 Pd incorporation into Cu_3btc_2 networks has been reported by the addition of Cu^{2+} sources to the solvothermal synthesis, but the resulting materials contain substantial Pd(0), in the form of entrapped nanoparticles: W. Zhang, Z. Chen, M. Al-Naji, P. Guo, S. Cwik, O. Halbherr, Y. Wang, M. Muhler, N. Wilde, R. Gläser and R. A. Fischer, *Dalton Trans.*, 2016, **45**, 14883.

