

PAPER

[View Article Online](#)
[View Journal](#) | [View Issue](#)

Cite this: *Polym. Chem.*, 2020, **11**, 7393

Sequence-defined L-glutamamide oligomers with pendant supramolecular motifs *via* iterative synthesis and orthogonal post-functionalization†

Marcin L. Ślęczkowski,^{a,b} Ian Segers,^b Yiliu Liu^{*a,b,c} and Anja R. A. Palmans^{id} ^{*a,b}

One of the great challenges in polymer chemistry is to achieve discrete and sequence-defined synthetic polymers that fold in defined conformations and form well-defined three-dimensional structures. Here, we present our progress to arrive at functional, sequence-defined and discrete oligomers by selecting a synthetic approach based on oligo-L-glutamamides. We introduce a solution-based iterative approach and start with an orthogonally protected L-glutamic acid derivative with an alkene or alkyne side chain. Using subsequent deprotection, activation and coupling steps, discrete, sequence-defined octamers were prepared with alkene or alkyne pendants at defined positions. Benzene-1,3,5-tricarboxamide (BTA) was selected as the supramolecular motif and decyl side chains for enhancing solubility. Full functionalization of the octamer was achieved with subsequent Cu(I)-catalyzed alkyne-azide and thiol-ene "click" chemistry, affording octamers with two BTA motifs at pre-defined positions. The octamers show a strong propensity to form hydrogen bonds in bulk as evidenced by infrared spectroscopy. In dilute solution, intermolecular aggregation of the amides present in the backbone and/or BTAs is observed. Our work shows that the iterative method serves as a reliable strategy for the synthesis of functionalized sequence-defined, discrete oligomers comprising side chain supramolecular motifs, although further optimizations are required.

Received 13th August 2020,
Accepted 1st November 2020

DOI: 10.1039/d0py01157f

rsc.li/polymers

Introduction

Technological applications of synthetic macromolecules have driven the field of polymer chemistry to a point in which seemingly every material can be synthesized.¹ Nowadays, the great variety in available polymerization methods combines a plethora of topologies with an immense choice of monomers, permitting unprecedented control over the functionalization density and molecular mass distribution of macromolecules.^{2–4} Yet, Nature is able to build hundreds of different types of functional proteins from only 20 different monomers.⁵ The secret of such diverse functionality of biomacromolecules lies in the precise control of the position of each monomer in the polymeric chain – sequence control.⁶ In

search of developing protein-like synthetic systems,⁷ polymer chemists have recently been particularly interested in the development of methodologies that allow controlling both the sequence as well as the molar mass.^{8,9} A recent excellent review on the progress made can be found in literature.¹⁰

Currently, two independent methodologies are applied to arrive at discrete, sequence-defined oligomers: solid-phase and liquid-phase. Solid-phase synthesis (SPS) was pioneered by Merrifield for peptide synthesis.^{11,12} This versatile approach enables the one by one build-up of oligomers by attaching monomers to the growing chain by using iterative chemical steps in a sequence-defined way. Owing to the versatility of conditions such as the used support,¹³ the concept of SPS evolved towards synthetic oligomers including nucleotides,^{14,15} peptoids,^{16,17} phosphodiesteres,¹⁸ amides,¹⁹ triazines,²⁰ and thiolactones.^{21,22} However, ultimate control of the reaction kinetics²³ as well as near quantitative yields²⁴ are required during the SPS to make the protocol applicable. As a result, most of the fixed solid-phase synthetic protocols approach their limits in terms of scalability and possibilities to incorporate more complex structures into the sequence-defined backbone chain.

The second method is based on a solution iterative (exponential or direct) growth strategy and originates from the syn-

^aInstitute for Complex Molecular Systems, Eindhoven University of Technology, P.O. Box 513, 5600 MB Eindhoven, The Netherlands. E-mail: liuyiliu@scut.edu.cn, a.palmans@tue.nl

^bLaboratory of Macromolecular and Organic Chemistry, Eindhoven University of Technology, P.O. Box 513, 5600 MB Eindhoven, The Netherlands

^cSouth China Advanced Institute for Soft Matter Science and Technology, South China University of Technology, 510640 Guangzhou, P. R. China


†Electronic supplementary information (ESI) available: Synthetic procedures, characterisation data and temperature-dependent CD measurements. See DOI: 10.1039/d0py01157f



thesis of dendrimers.^{25–27} This strategy has been successfully applied to prepare a manifold of discrete, linear oligomers.^{10,28} While the direct growth strategy enables to attach a monomer or a short chain depending on the building blocks,^{29–32} in the iterative exponential strategy each coupling step doubles the length of growing chain.²⁸ The iterative exponential growth strategy, also known as the orthogonal iterative divergent/convergent approach, makes use of bifunctional monomers with orthogonally protected end-groups. The end-groups can be separately deprotected (the divergent part) and subsequently coupled with each other (the convergent part) giving an orthogonally protected dimer. The same steps can be repeated with the obtained dimer, resulting in an exponential growth of the chain. However, the required orthogonality of the protecting end-groups reduces the diversity of applicable monomers

and requires chemical conversions that are compatible with each other. Nonetheless, elegant approaches show that discrete oligomers can be built up using a variety of linkages (triazoles,^{33–35} esters,^{36–41} or amides^{42–45}) and affording high degrees of polymerizations.

This work explores the scope and limitations of a solution-based approach to sequence-defined oligomers with pendant H-bonding motifs at predefined positions. We select an L-γ-glutamamide backbone as the scaffold holding propargylamide and trisallyloxyamide units (Scheme 1), and synthesize octamers with different sequences of monomers along the backbone with an iterative exponential growth strategy. We further show successful orthogonal post-functionalization *via* subsequent copper(i) catalyzed azide-alkyne cycloaddition (CuAAC) and radical thiol-ene addition. As supramolecular H-bonding motif, we select the benzene-1,3,5-tricarboxamide (BTA) unit. BTAs form one-dimensional, helical H-bonded aggregates⁴⁶ and were used previously to drive the assembly of macromolecules into (single-chain) polymeric nanoparticles.⁴⁷ BTAs are considered as a *functional* motif because of their ability to induce higher order structures, making them interesting as a test case to induce functionality into sequence defined oligomers. Ultimately, this will allow us to assess in how far properties of the oligomers are affected by the exact position of the functional side chain. The structures of all oligomers were analyzed by nuclear magnetic resonance (NMR) and mass (MS) spectroscopy, and their behavior was characterized by infrared (IR) spectroscopy in the solid state and circular dichroism (CD) spectroscopy in dilute solution.

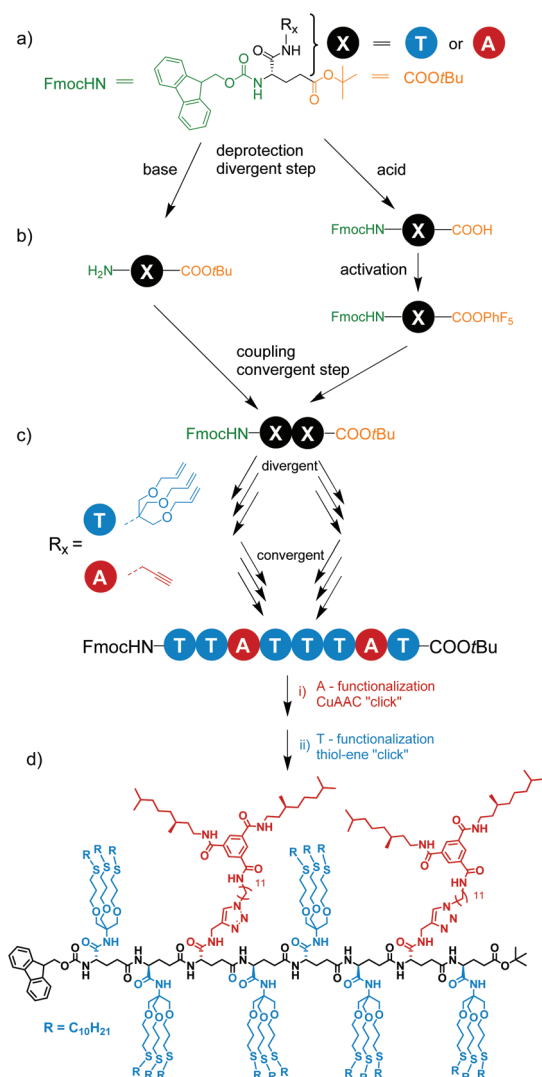

Scheme 1 (a) Monomer design for the synthesis of L-γ-glutamamide-based octamer; (b) deprotection and amide coupling steps for the synthesis of a dimer; (c) schematic representation of the synthesis of the octamer; (d) post-functionalization of the octamer *via* CuAAC and thiol-ene "click" chemistry.

Results and discussion

Monomer design and synthetic approach

Our selected iterative synthesis strategy of the sequence-defined octamer is shown in Scheme 1 and requires a monomer with a side chain, and two different types of end-groups. After careful evaluation, L-glutamic acid, comprising two acid functions and one amine function, was identified as a suitable monomer that fulfilled all requirements (Scheme 1a). L-Glutamic acid is commercially available with the amine group protected with fluorenylmethyloxycarbonyl (Fmoc) and the γ-carboxylic acid protected with *tert*-butoxy (*t*BuO). Whereas the *t*BuO is acid-labile, but base-stable, the Fmoc group is base-labile, but acid-stable (Scheme 1b). Free amine and acid groups can be readily coupled with the use of an acid activating agents to create an amide bond (Scheme 1c), and by repetitive deprotection and coupling steps the oligomers can be built up. Finally, orthogonal post-functionalization of the final oligomer backbone can be achieved *via* the α-carboxylic acid, modified with a functionalized group that has to react in high yields at the final steps of the synthesis (post-functionalization strategy). Thus, terminal alkyne and alkene bonds were selected as these are stable under the deprotection conditions and during amide formation but can be independently reacted using sequential CuAAC and radical





Scheme 2 Synthesis of monomers **2** and **3**. Reaction conditions: (i) propargylamine, EDC-HCl/HOBT·xH₂O, DIPEA, THF, overnight at room temperature, 53%; (ii) tris[(allyloxy)methyl]aminomethane, EDC-HCl/HOBT·xH₂O, DIPEA, THF, overnight at room temperature, 67%.

thiol-ene addition (Scheme 1d). To introduce alkene and alkyne functionalities, we selected propargylamine and tris[(allyloxy)methyl]aminomethane (Scheme 2). The latter was selected to ensure sufficient solubility of the monomer and subsequent oligomers.

Monomer synthesis

The synthesis of the two starting monomers with either alkene or alkyne pendants is shown in Scheme 2. The 1,2,3-tris(allyloxy) group was synthesized in 3 steps starting from 2-amino-2-(hydroxymethyl)-1,3-propanediol following a route published before.^{48,49} Commercially available *N*-protected and α_{COOH} -protected γ -glutamic acid **1** was modified with either commercially available propargylamine or tris[(allyloxy)methyl]aminomethane to yield monomers **2** and **3**, respectively. The activation of the α -COOH in Fmoc-Glu(OtBu)-OH was achieved by *N*-(3-dimethylaminopropyl)-*N'*-ethylcarbodiimide hydrochloride (EDC-HCl) and 1-hydroxybenzotriazole hydrate (HOBT·xH₂O). The activated acid readily reacted with either propargylamine or tris[(allyloxy)methyl]aminomethane giving propargylamide (**2**) or trisallyloxy-*tert*-butylamide (**3**) as a side

groups on the protected γ -glutamic acid. Partial undesired deprotection of Fmoc-protecting group by *N,N*-diisopropylethylamine (DIPEA) was observed, leading to a decrease in the yield. Monomers **2** and **3** were purified *via* column chromatography and isolated in yields of 53% and 67%, respectively. Since we did not isolate unprotected/activated intermediates, the yields of deprotection/activation steps have not been determined. Throughout this work the monomer or residue with the alkyne containing side group will be defined as an *A*, while the monomer or residue with the trisallyloxy-*tert*-butylamide side group will be defined as a *T*.


Synthesis of L- γ -glutamamide-based octamers

In the first iterative step we synthesized dimers. Hereto, monomers **2** and **3** were selectively deprotected by removing either the Fmoc-protecting group or the *t*BuO protecting group. Monomers **2** and **3** were treated with TFA to remove the *t*BuO-protecting group, giving free carboxylic acids (**4a** and **6a**). Next, the addition of pentafluorophenyl trifluoroacetate to these two intermediates in the presence of DIPEA activated the acids to pentafluorophenyl esters **4b** and **6b**. In parallel to this, monomer **3** was treated with diethylamine to remove the Fmoc-protecting group, affording monomer **5** with a terminal free amine. The isolation of free amine monomer **5** (81%) was accomplished using column chromatography. Intermediate compounds **4b** and **5**, and compounds **5** and **6b** reacted readily with each other in DMF giving dimers FmocHN-AT-COOtBu (**7**) and a FmocHN-TT-COOtBu (**8**) (Scheme 3). Dimers **7** (80%) and **8** (74%) were purified by column chromatography and their structures were confirmed by ¹H NMR, ¹³C NMR, and Maldi-ToF MS (Fig. S1–6, ESI†). Subsequently, dimers **7** and **8** were deprotected and activated to yield **9** and **10b** (Scheme 4a). Subsequent coupling in DMF, in a similar fashion as was done to obtain the dimers, afforded tetramer FmocHN-TTAT-COOtBu (**11**) in a yield of 60% after column chromatography.



Scheme 3 Synthesis of dimers **7** and **8**. Reaction conditions: (i) TFA, DCM, 3 h at room temperature; (ii) pentafluorophenyl trifluoroacetate, DIPEA, CHCl₃, 1–3 h at room temperature; (iii) diethylamine, DCM, 3 h at room temperature, 81%; (iv) DMF, 0.5–1.5 h at room temperature, 80% (for **7**) and 74% (for **8**).



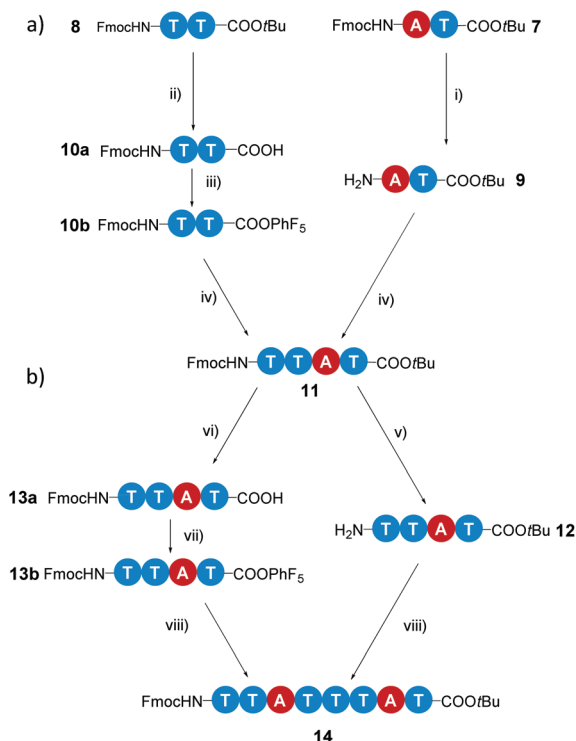

Scheme 4 Schematic representation for the synthesis of (a) tetramer **11** and (b) octamer **14**. Reaction conditions: (i) diethylamine, DCM, 3 h at room temperature; (ii) TFA, DCM, overnight at room temperature; (iii) pentafluorophenyl trifluoroacetate, DIPEA, CHCl_3 , 1 h at room temperature; (iv) DMF, 1 h at room temperature, 60%; (v) piperidine, CHCl_3 , 1 h at room temperature; (vi) TFA, CHCl_3 , overnight at room temperature; (vii) pentafluorophenyl trifluoroacetate, DIPEA, CHCl_3 , 2 h at room temperature; (viii) DMF, 1 h at room temperature, 39%.

Further, deprotected tetramers **12** and **13a** were obtained upon treatment of the tetramer **11** with either piperidine or TFA. Free acid **13a** was activated with pentafluorophenyl trifluoroacetate to yield **13b** which was subsequently coupled with **12** to yield octamer FmocHN-TTATTTAT-COOtBu (**14**) (Scheme 4b). The moderate yield of the final coupling (39%) was caused by the decreasing solubility of the tetramers. Octamer **14** was isolated by column chromatography and its structure was confirmed by ^1H NMR, ^{13}C NMR, and Maldi-ToF MS (Fig. 1, and Fig. S7, ESI†). The Maldi-ToF MS spectrum in Fig. 1a shows one peak at m/z 2765.5, consistent with the Na^+ adduct of the octamer. Together with the observation that Maldi-ToF MS shows a similar sensitivity towards (partially) deprotected octamers (*vide infra* for octamer **15**) and tetramers (see ESI†), this strongly points to the absence of lower oligomers and the presence of both protecting groups. The ^1H NMR spectrum in DMSO- d_6 (Fig. 1b) shows proton signals that are relatively sharp, which can all be assigned.

The route we selected, readily permits to make octamers of different sequence by judicious choice in deprotecting the tetramers, followed by acid activation and the amide coupling reaction. In a similar fashion as FmocHN-TTATTTAT-COOtBu (**14**) was prepared, two octamers having different sequences

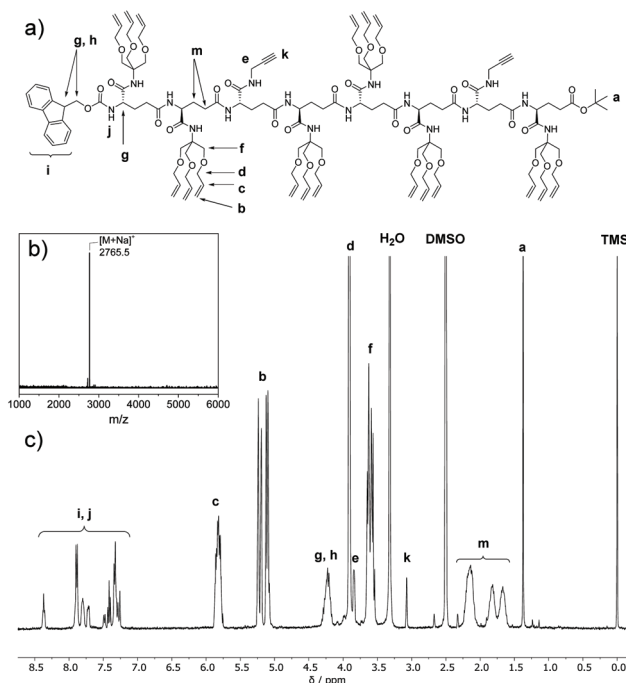


Fig. 1 (a) Chemical structure of **14**; (b) Maldi-ToF MS and; (c) ^1H NMR spectrum (400 MHz, DMSO- d_6) of octamer **14** (FmocHN-TTATTTAT-COOtBu).

(FmocHN-TATTTAT-COOtBu (**15**) and FmocHN-TTATTTAT-COOtBu (**16**)) were prepared using the same synthetic procedures (Scheme S1, ESI†). This approach shows that by small changes in the coupling sequence, different topologies are easily accessible.

During the synthesis of all three octamers, we observed a significant drop in the yield during the last amide coupling reaction. The decrease in solubility already arises during the activation of the carboxylic acid group in the tetramers to the pentafluorophenyl ester. Increasing the chain length results in a further decrease in solubility, possibly as a result of the increasing number of backbone amide groups that may enhance the propensity to form hydrogen bonds and hereby increases the overall backbone rigidity. In fact, semi-crystalline polyamides such as Nylon-6,6 are hardly soluble in most of the organic solvents, also in polar aprotic solvents like DMF. The fact that the carboxylic acid group can also participate in the intermolecular hydrogen bonds potentially decreases its nucleophilic character and suppresses the activation to the pentafluorophenyl ester. Also, the solubility of the terminal free amine tetramers in chlorinated solvents and in DMF decreased. This, in combination with the use of not fully purified intermediates, resulted in incomplete conversion and the appearance of byproducts (for example FmocHN-TTAT-CO-N-piperidiny) during the amide coupling reactions. Besides the appearance of side products, mass analysis showed the presence of unreacted substrates in the crude mixture of the amide couplings. Extensive column chromatography was required to purify the octamers. Maldi-ToF MS showed that the terminal



Polym. Chem., 2020, 11, 7393–7401 | 7397



Scheme 6 Synthesis of bis((S)-BTA)-hexa(tris(decylallyloxy))Fmoc-(TTAT₂)-COOtBu (**24**). Reagents and conditions: (i) (1) BTA-azide **20**, CuSO₄, sodium ascorbate, DMSO, 50 °C → room temperature, argon atmosphere, overnight at room temperature; (2) CuSO₄, sodium ascorbate, DMSO, 50 °C → RT, argon flow, 2 days at room temperature, 37%; (ii) 1-decanethiol, DMPA, DMA, *hν*, argon, 4 h at room temperature, 31%.

Self-assembly of the L-γ-glutamamide oligomers in solid state and in solution

The poor solubility of the octamers before functionalization suggested that the growing backbone favors formation of intermolecular hydrogen bonds that cause aggregation. Infrared (IR) spectroscopy in solid state showed absorption bands at 3275 cm⁻¹ (ν_{N-H}), 1729 cm⁻¹, 1691 cm⁻¹, 1661 cm⁻¹ (amide I) and 1533 cm⁻¹ (amide II) for tetramer **11** and octamer **14** (Fig. 2a). The position of these bands suggests the presence of hydrogen bonds with a similar pattern in both oligomers.⁵¹

The thermal behavior of the oligomers was studied by polarized optical microscopy (POM) and differential scanning calorimetry (DSC), and a reversible transition for tetramer **11** at 220 °C was observed with a low enthalpy of $\Delta H = 360 \text{ J mol}^{-1}$ (Fig. 2b). This transition was accompanied by the disappearance of the texture under crossed polarizers, which suggests a melting transition (Fig. S11, ESI†). The low enthalpy of the transition suggests a low degree of crystallinity in the oligomer. None of the octamers showed any transitions in DSC nor birefringence in POM when using crossed polarizers. The combined results of IR, DSC and POM of octamer **14** suggest that very stable structures are formed in the solid state with clearing



Fig. 2 (a) IR spectra of tetramer **11** (red) and octamer **14** (black) in solid state; (b) DSC thermogram of tetramer **11** recorded at 10 °C min⁻¹; (c) IR spectra of functionalized octamers **23** (black) and **24** (red) in the solid state; (d) CD spectra of octamers **23** (black, in DCE) and **24** (blue, in MCH), (*c* = 25 μM, *T* = 20 °C, *l* = 1 cm).

temperatures above 200 °C. However, most likely due to multiple possible conformations staying in thermodynamic equilibrium, there is no long-range order as suggested by POM.⁵² In conclusion, both tetramer **11** and octamer **14** showed the presence of hydrogen bonds, however the lack of long-range order suggests the presence of multiple competing supramolecular structures making a more detailed insight in the organization of the materials in the solid state challenging.

To assess, whether functionalization of the octamers with BTA and decyl chains reflects on the properties of the solid state materials, we recorded IR spectra of functionalized octamers **23** and **24**. Interestingly, the pattern does not change substantially, indicating that neither of the attached units have a large influence on the supramolecular structure (Fig. 2c). H-bond stabilized BTA aggregates show characteristic absorption bands at 3226 cm⁻¹ (ν_{N-H}), 1636 cm⁻¹ (amide I) and 1548 cm⁻¹ (amide II).⁵³ Unfortunately, these absorption bands are at the same position as those arising from the backbone amides of the oligomers (Fig. 2a). Since the backbone amides have a higher concentration, the extent to which BTAs are engaged in hydrogen bonding can not be assessed. Similar to octamer **14**, functionalized octamers **23** and **24** showed no birefringence and no transitions in DSC. Functionalization of the octamers did not result in a visible change of the solid state properties. We anticipated that functionalization should impact the solubility of the octamers, thus further characterization was performed in dilute solutions.

To study the behavior of the octamers in dilute solutions, we used circular dichroism (CD) spectroscopy. Due to the intrinsic low solubility in apolar solvents, CD spectra of octamer **23**, functionalized with two BTAs, were recorded in 1,2-dichloroethane



(DCE). On the contrary, octamer **24**, functionalized with 2 BTAs and 18 decyl chains was soluble in apolar methyl cyclohexane (MCH). As a reference, we recorded also the CD spectrum of octamer **14**, which shows a weak maximum around 255 nm followed by negative CD effect with an extremum around 228 nm (Fig. S12a, ESI†). The CD signal originates from presence of stereocenters with all *S*-configuration adjacent to the amide chromophore. The CD spectra of functionalized octamers **23** and **24** were measured after slow cooling ($1\text{ }^{\circ}\text{C min}^{-1}$) from $90\text{ }^{\circ}\text{C}$ to $20\text{ }^{\circ}\text{C}$, and showed only one extremum at 230 nm, suggesting that the presence of BTAs leads to the formation of a different superstructure. A significantly stronger dichroic response of -50 mdeg was observed for the octamer **23** in DCE, a solvent where BTAs are normally molecularly dissolved. The aggregation of the BTAs in this case may be permitted by low solubility of the oligomeric backbone or is combined with the intermolecular aggregation of the backbone amides.⁵⁴ On the other hand, octamer **24** shows hardly any CD signal (-15 mdeg) compared to the other 2 octamers, even though it was dissolved apolar MCH.

To further unravel the origin of the observed CD signal, we also measured variable-temperature CD (VT-CD) of the octamers (Fig. S12b, ESI†). We found that at high temperatures the CD signal is always present and around -10 mdeg . This signal most likely arises from the amide chromophores along the backbone and not from the BTA unit. Octamer **23** shows a clear onset of the CD increase around $50\text{ }^{\circ}\text{C}$, which can correspond to intermolecular BTA aggregation and/or aggregation of the amides of the oligomers. The temperature-independent signal of octamer **24** suggests that presumably no BTA aggregation is present in dilute solution. This can be a result of dense side-chain functionalization with the bulky decyl chains, which in turn effectively hampers BTA aggregation.

The results indicate that the aggregation of the BTAs in such complex systems is possible, but difficult to control when multiple binding sites compete with each other and the interactions of all the components with the solvent are not balanced. Therefore, we conclude that the combination of poorly soluble oligoamides in the backbone with a BTA motif is not an optimal design for controlled folding of sequence-defined macromolecules. Finally, the intrinsic absorption of the light of similar energy by multiple parts of the molecule impedes to unravel which chromophore contributes to which aggregation process.

Conclusions

We have demonstrated the successful synthesis of orthogonally protected γ -glutamamide octamers, containing alkyne- and alkene-based reactive side groups *via* a multi-step synthesis. Increasing the chain length resulted in decreasing solubility and reactivity, and a concomitant decrease in yield was observed. All in all, the solution-based strategy developed here allows to access sequence-defined oligomers of defined stereochemistry and with reactive handles at selected positions in overall yields of 12–15%. The reaction times of the deprotection, activation and coupling steps are relatively short. The most time-consuming step is

column chromatography, and the optimization required for the purification steps. Finally, the synthetic procedures developed here are scalable to multigram scale. For example, the synthesis of the octamers afforded 1 g of end product.

Orthogonal post-functionalization of one of the octamers was successfully achieved with bis(*S*)-3,7-dimethyloctyl-(11-azidoundecyl)-BTA *via* a CuAAC reaction. Subsequently, full functionalization with solubilizing decyl chains was achieved using a radical thiol-ene addition. Furthermore, the herein synthesized oligomers formed secondary structures arising from hydrogen-bond formation in bulk as well as in dilute solutions. The initial characterization showed that despite the molecular complexity, BTA aggregation is possible in these molecules, however, improved molecular engineering is required to assess this system's particular assembly features.

Our results show that synthesis of sequence-defined oligomers holding supramolecular motifs at defined positions is possible. However, further optimization and reconsideration of the strategy and supramolecular units used is required for this approach to become applicable in the synthesis of functional, sequence-defined oligomers with high degrees of polymerization. Iterative approaches based on classical organic synthesis offer opportunities to access sequence-defined oligomers in few steps with satisfying yields and amounts. The post-functionalization strategy does not require a large excess of the reagents, in contrast to the solid-phase approach, and is therefore feasible to synthesize the oligomers in amounts permitting further modification and analysis. These advantages make that iterative solution-based approaches can offer an alternative to complement the frequently applied solid-phase strategies. While SPS method is difficult to outperform in the large scale synthesis of complex and long peptides, synthesis of non-natural oligomers in scales exceeding 1 gram remains a challenge.

The major drawback of the monomers selected here is the decreasing solubility of the backbone, which makes further elongation difficult and currently precludes isolation of the oligomers longer than the octamer in reasonable yields. To overcome the solubility issue, we will focus in the future on the pre-functionalization of the “*T* (olefin)” monomer with solubilizing side chains prior to the oligomer chain build-up. This should improve the solubility of the oligomers, hereby improving the reactivity. In addition, a supramolecular motif with the absorption maximum outside the absorption range of peptide bonds is also under consideration. We are currently following this strategy to synthesize longer oligomers.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors like to thank Prof. E.W. Meijer for continued support and the EUROSEQUENCES community for fruitful dis-



cussions about this project. This work was supported by the European Union's Horizon 2020 research and innovation program (Marie Skłodowska-Curie grant agreement No 642083). Y.L. acknowledges the support from the National Natural Science Foundation of China (21901077) and Guangdong Provincial Key Laboratory of Functional and Intelligent Hybrid Materials and Devices (No. 2019B121203003).

References

- G. Polymeropoulos, G. Zapsas, K. Ntetsikas, P. Bilalis, Y. Gnanou and N. Hadjichristidis, *Macromolecules*, 2017, **50**, 1253–1290.
- K. Matyjaszewski and J. Xia, *Chem. Rev.*, 2001, **101**, 2921–2990.
- R. B. Grubbs and R. H. Grubbs, *Macromolecules*, 2017, **50**, 6979–6997.
- S. Perrier, *Macromolecules*, 2017, **50**, 7433–7447.
- A. Saint-Léger, C. Bello, P. D. Dans, A. G. Torres, E. M. Novoa, N. Camacho, M. Orozco, F. A. Kondrashov and L. Ribas de Pouplana, *Sci. Adv.*, 2016, **2**, e1501860.
- T. N. Starr and J. W. Thornton, *Nat. Biotechnol.*, 2017, **35**, 125–126.
- J. P. Cole, A. M. Hanlon, K. J. Rodriguez and E. B. Berda, *J. Polym. Sci., Part A: Polym. Chem.*, 2017, **55**, 191–206.
- J.-F. Lutz, M. Ouchi, D. R. Liu and M. Sawamoto, *Science*, 2013, **341**, 1238149–1238149.
- J.-F. Lutz, *Macromol. Rapid Commun.*, 2017, **38**, 1700582.
- S. C. Solleder, R. V. Schneider, K. S. Wetzel, A. C. Boukis and M. A. R. Meier, *Macromol. Rapid Commun.*, 2017, **38**, 1600711.
- B. Merrifield, *Science*, 1986, **232**, 341–347.
- R. B. Merrifield, *J. Am. Chem. Soc.*, 1963, **85**, 2149–2154.
- L. Oswald, A. Al Ouahabi, C. Laure, J. Amalian, L. Charles and J. Lutz, *J. Polym. Sci., Part A: Polym. Chem.*, 2019, **57**, 403–410.
- T. G. W. Edwardson, K. M. M. Carneiro, C. J. Serpell and H. F. Sleiman, *Angew. Chem., Int. Ed.*, 2014, **53**, 4567–4571.
- S. L. Beaucage and R. P. Iyer, *Tetrahedron*, 1992, **48**, 2223–2311.
- A. S. Knight, E. Y. Zhou, M. B. Francis and R. N. Zuckermann, *Adv. Mater.*, 2015, **27**, 5665–5691.
- R. N. Zuckermann, J. M. Kerr, S. B. H. Kent and W. H. Moos, *J. Am. Chem. Soc.*, 1992, **114**, 10646–10647.
- N. F. König, A. Al Ouahabi, S. Poyer, L. Charles and J.-F. Lutz, *Angew. Chem., Int. Ed.*, 2017, **56**, 7297–7301.
- Z. Wan, Y. Li, S. Bo, M. Gao, X. Wang, K. Zeng, X. Tao, X. Li, Z. Yang and Z. X. Jiang, *Org. Biomol. Chem.*, 2016, **14**, 7912–7919.
- J. W. Grate, K.-F. Mo and M. D. Daily, *Angew. Chem., Int. Ed.*, 2016, **55**, 3925–3930.
- P. Espeel, L. L. G. Carrette, K. Bury, S. Capenberghs, J. C. Martins, F. E. Du Prez and A. Madder, *Angew. Chem., Int. Ed.*, 2013, **52**, 13261–13264.
- S. Martens, J. Van den Begin, A. Madder, F. E. Du Prez and P. Espeel, *J. Am. Chem. Soc.*, 2016, **138**, 14182–14185.
- P. Espeel and F. E. Du Prez, *Eur. Polym. J.*, 2015, **62**, 247–272.
- J. M. Palomo, *RSC Adv.*, 2014, **4**, 32658–32672.
- S. M. Grayson and J. M. J. Fréchet, *Chem. Rev.*, 2001, **101**, 3819–3867.
- C. J. Hawker and J. M. J. Frechet, *J. Am. Chem. Soc.*, 1990, **112**, 7638–7647.
- D. A. Tomala, H. Baker, J. Dewald, M. Hall, G. Kallos, S. Martin, J. Roeck, J. Ryder and P. Smith, *Polym. J.*, 1985, **17**, 117–132.
- S. Binauld, D. Damiron, L. A. Connal, C. J. Hawker and E. Drockenmuller, *Macromol. Rapid Commun.*, 2011, **32**, 147–168.
- N. Franz, G. Kreutzer and H.-A. Klok, *Synlett*, 2006, 1793–1815.
- S. C. Solleder, K. S. Wetzel and M. A. R. Meier, *Polym. Chem.*, 2015, **6**, 3201–3204.
- M. Porel and C. A. Alabi, *J. Am. Chem. Soc.*, 2014, **136**, 13162–13165.
- S. C. Solleder and M. A. R. Meier, *Angew. Chem., Int. Ed.*, 2014, **53**, 711–714.
- S. Binauld, C. J. Hawker, E. Fleury and E. Drockenmuller, *Angew. Chem., Int. Ed.*, 2009, **48**, 6654–6658.
- J. C. Barnes, D. J. C. Ehrlich, A. X. Gao, F. A. Leibfarth, Y. Jiang, E. Zhou, T. F. Jamison and J. A. Johnson, *Nat. Chem.*, 2015, **7**, 810–815.
- J. Li, M. Leclercq, M. Fossepré, M. Surin, K. Glinel, A. M. Jonas and A. E. Fernandes, *Polym. Chem.*, 2020, **11**, 4040–4046.
- M. B. Koo, S. W. Lee, J. M. Lee and K. T. Kim, *J. Am. Chem. Soc.*, 2020, **142**, 14028–14032.
- N. Franz, L. Menin and H. A. Klok, *Eur. J. Org. Chem.*, 2009, 5390–5405.
- D. Seebach and M. G. Fritz, *Int. J. Biol. Macromol.*, 1999, **25**, 217–236.
- K. Takizawa, C. Tang and C. J. Hawker, *J. Am. Chem. Soc.*, 2008, **130**, 1718–1726.
- K. Takizawa, H. Nulwala, J. Hu, K. Yoshinaga and C. J. Hawker, *J. Polym. Sci., Part A: Polym. Chem.*, 2008, **46**, 5977–5990.
- G. Brooke, N. Cameron, J. A. MacBride and M. Whiting, *Polymer*, 2002, **43**, 1139–1154.
- C. Bao, B. Kauffmann, Q. Gan, K. Srinivas, H. Jiang and I. Huc, *Angew. Chem., Int. Ed.*, 2008, **47**, 4153–4156.
- S. S. Reddy, X. Dong, R. Murgasova, A. I. Gusev and D. M. Hercules, *Macromolecules*, 1999, **32**, 1367–1374.
- G. M. Brooke, S. Mohammed and M. C. Whiting, *J. Chem. Soc., Perkin Trans. 1*, 1997, 3371–3380.
- G. Brooke, J. A. Hugh MacBride, S. Mohammed and M. Whiting, *Polymer*, 2000, **41**, 6457–6471.
- S. Cantekin, T. F. A. de Greef and A. R. A. Palmans, *Chem. Soc. Rev.*, 2012, **41**, 6125.
- G. M. Huurne, A. R. A. ter Palmans and E. W. Meijer, *CCS Chem.*, 2019, 64–82.



- 48 C. T. Seto, J. P. Mathias and G. M. Whitesides, *J. Am. Chem. Soc.*, 1993, **115**, 1321–1329.
- 49 M. Segura, F. Sansone, A. Casnati and R. Ungaro, *Synthesis*, 2001, 2105–2112.
- 50 M. L. Ślęczkowski, E. W. Meijer and A. R. A. Palmans, *Macromol. Rapid Commun.*, 2017, **38**, 1700566.
- 51 A. Barth, *Biochim. Biophys. Acta, Bioenerg.*, 2007, **1767**, 1073–1101.
- 52 M. Kudo, V. Maurizot, H. Masu, A. Tanatani and I. Huc, *Chem. Commun.*, 2014, **50**, 10090–10093.
- 53 P. J. M. Stals, M. M. J. Smulders, R. Martín-Rapún, A. R. A. Palmans and E. W. Meijer, *Chem. – Eur. J.*, 2009, **15**, 2071–2080.
- 54 T. Mes, R. van der Weegen, A. R. A. Palmans and E. W. Meijer, *Angew. Chem.*, 2011, **123**, 5191–5195.

