


 Cite this: *RSC Adv.*, 2020, 10, 1351

# $\alpha(\beta)$ -PbO<sub>2</sub> doped with Co<sub>3</sub>O<sub>4</sub> and CNT porous composite materials with enhanced electrocatalytic activity for zinc electrowinning†

 Xuanbing Wang,<sup>ab</sup> Ruidong Xu,<sup>\*ab</sup> Suyang Feng,<sup>ab</sup> Bohao Yu<sup>ab</sup> and Buming Chen<sup>b</sup>

The high energy consumption during zinc electrowinning is mainly caused by the high overpotential of the oxygen evolution for Pb–Ag alloys with strong polarization. The preparation of new active energy-saving materials has become a very active research field, depending on the synergistic effects of active particles and active oxides. In this research, a composite material,  $\alpha(\beta)$ -PbO<sub>2</sub>, doped with Co<sub>3</sub>O<sub>4</sub> and CNTs on the porous Ti substrate was prepared *via* one-step electrochemical deposition and the corresponding electrochemical performance was investigated in simulated zinc electrowinning solution. The composite material showed a porous structure, finer grain size and larger electrochemical surface area (ECSA), which indicated excellent electrocatalytic activity. Compared with the Pb–0.76 wt% Ag alloy, the overpotential of oxygen evolution for the 3D-Ti/PbO<sub>2</sub>/Co<sub>3</sub>O<sub>4</sub>–CNTs composite material was decreased by about 452 mV under the current density of 500 A m<sup>-2</sup> in the simulated zinc electrowinning solution. The decrease in the overpotential of oxygen evolution was mainly ascribed to the higher ECSA and lower charger transfer resistance. Moreover, it showed the lowest self-corrosion current density of 1.156 × 10<sup>-4</sup> A cm<sup>-2</sup> and may be an ideal material for use in zinc electrowinning.

 Received 3rd October 2019  
 Accepted 16th November 2019

DOI: 10.1039/c9ra08032e

[rsc.li/rsc-advances](http://rsc.li/rsc-advances)

## 1. Introduction

Globally, 80% of zinc is produced by zinc hydrometallurgy, for which 80% of the energy consumption originates from the electrowinning procedure. The Pb–(0.5–1 wt%)Ag alloy anode is widely used as an insoluble anode because it is conductive and relatively stable in rigorous working media. However, its high overpotential for oxygen evolution and high cost due to the addition of Ag are still unacceptable. In the past few years, extensive attempts have been devoted to the design of high electrocatalytic activity Pb–Ag based composited anodes and the electrocatalytic activity was greatly improved when some precious metals oxides were added.<sup>1,2</sup>

The oxygen evolution reaction (OER) plays a crucial role in hydrogen production and zinc electrowinning (ZW) and the sluggish OER kinetics always presents a challenge. Although some precious metals have shown great electrocatalytic activity for the OER in strongly acidic media, their high cost still limits their applications in industry. Therefore, the development of

base metal electrode materials with superior electrocatalytic activity and higher stability is urgently needed. Lead dioxide (PbO<sub>2</sub>) has drawn much attention due to its good electrical conductivity, low cost and high resistance to corrosion.<sup>3</sup> However, there are still some drawbacks such as high overpotential for oxygen evolution, low stability, and low electrocatalytic activity in view of its limited active surface.<sup>4</sup> To solve these problems, some researchers have made unremitting efforts to prepare modified PbO<sub>2</sub> anodes with active coatings, such as RuO<sub>2</sub>,<sup>5</sup> IrO<sub>2</sub>,<sup>6</sup> Ta<sub>2</sub>O<sub>5</sub>,<sup>7</sup> MnO<sub>2</sub>,<sup>8</sup> Co<sub>3</sub>O<sub>4</sub> (ref. 4) and carbon nanotubes (CNTs).<sup>9</sup>

The PbO<sub>2</sub> electrode with excellent electrocatalytic activity and stability requires two key conditions. The first is a highly active surface, which is beneficial for the interface electrochemical reaction; the second is the stability of its physical structure. In order to obtain a highly active surface, the O<sub>2</sub> bubble-templated deposition of a porous oxide was explored and a novel method to prepare PbO<sub>2</sub> electrodes modified by MnO<sub>2</sub> and Co<sub>3</sub>O<sub>4</sub> was developed. The study showed that the porous electrode could provide more surface area, which is desirable for the electrode capacity.<sup>10–14</sup>

As is known, porous titanium is used as the electrode substrate material due to its good electrical conductivity, high surface area and excellent corrosion resistance.<sup>15</sup> Comparative studies of the PbO<sub>2</sub> electrode on the plate-like and porous Ti substrates were reported, and higher electrocatalytic performance was obtained.<sup>16,17</sup> A porous Ti/SnO<sub>2</sub>–Sb<sub>2</sub>O<sub>3</sub>–CNT/PbO<sub>2</sub>

<sup>a</sup>State Key Laboratory of Complex Nonferrous Metal Resources Clean Utilization, Kunming University of Science and Technology, Kunming 650093, China. E-mail: [rdxupaper@aliyun.com](mailto:rdxupaper@aliyun.com); Fax: +86 871 65161278; Tel: +86 871 65160072

<sup>b</sup>Faculty of Metallurgical and Energy Engineering, Kunming University of Science and Technology, Kunming 650093, China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c9ra08032e



electrode was prepared by thermal decomposition and electro-deposition technology, in which PbO<sub>2</sub> coating covered the surface of porous Ti and formed a fine crystalline structure, possessing a longer service life.<sup>18</sup> Another nanostructured 3D-Ti/Sb-SnO<sub>2</sub>-Gr electrode was fabricated by a fast-evaporation process, which achieved a great enhancement in the structure and electrochemical performance, especially in its electrocatalytic activity.<sup>19</sup>

Sulfonate medium has been widely used as an environmentally friendly electrolyte in nickel deposition but is seldom reported for PbO<sub>2</sub> electrodeposition.<sup>20</sup> Co<sub>3</sub>O<sub>4</sub> is attractive in the electrocatalytic field due to its excellent electrocatalytic activity. In addition, CNTs provide a promising strategy for boosting the conductivity of semiconductors with wide band gaps, or insulators.<sup>21</sup> In this study, in order to obtain a material with a lower oxygen evolution reaction overpotential, higher active surface area and higher electrocatalytic properties,  $\alpha(\beta)$ -PbO<sub>2</sub> doped with Co<sub>3</sub>O<sub>4</sub> and CNT porous composite materials on a porous Ti substrate was prepared from an electrolyte of Pb(CH<sub>3</sub>COO)<sub>2</sub>-NH<sub>2</sub>SO<sub>3</sub>H. The phase structures and surface microstructures were investigated by XRD and FE-SEM, the electrocatalytic activity was evaluated by anodic polarization, CV and EIS, and the corrosion resistance was also tested by Tafel plots.





## 2. Experimental

### 2.1 Preparation of porous composite materials

Firstly, porous titanium substrates (20 mm × 10 mm × 1 mm) with an average pore size of 100 μm were mechanically polished and then cleaned with deionized water and acetone to remove solid impurities. After that, they were degraded with 10 wt% sodium hydroxide (NaOH) solution, etched in boiling hydrochloric acid (HCl) with concentration 30 wt% for 60 min, and then washed by ultrasonication in deionized water.

3D-Ti/PbO<sub>2</sub>, 3D-Ti/PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub>, 3D-Ti/PbO<sub>2</sub>-CNTs and 3D-Ti/PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub>-CNTs composite materials were prepared *via* anode electrodeposition from an electrolyte of Pb(CH<sub>3</sub>COO)<sub>2</sub>-NH<sub>2</sub>SO<sub>3</sub>H. The basic electrolyte composition included 0.2 M Pb(CH<sub>3</sub>COO)<sub>2</sub> and a certain amount of H<sub>2</sub>NSO<sub>3</sub>H to adjust the pH value of the solution (1.0). For the doped materials, the concentrations of the second phase particles Co<sub>3</sub>O<sub>4</sub> and CNTs were controlled at 10 g L<sup>-1</sup> and 0.5 g L<sup>-1</sup>, respectively. The electrodeposition process conditions were as follows: current density, 20 mA cm<sup>-2</sup>; bath temperature, 40 ± 2 °C; deposition time, 60 min. For the doped materials, Co<sub>3</sub>O<sub>4</sub> and CNTs were processed by ultrasound for 30 min before the electrodeposition. In addition, for the CNTs doped materials, 0.01 M surfactant sodium dodecyl sulfate (C<sub>12</sub>H<sub>25</sub>SO<sub>3</sub>Na, SDS) was added during the ultrasonic treatment. During the electrodeposition, mild stirring of 400 rpm to 600 rpm was carried out using a magnetic stirrer. After the electrodeposition, the composite materials were rinsed with deionized water and dried under vacuum for further characterization.

The forming mechanism of PbO<sub>2</sub> was reported by Feischman and it has been widely accepted. The detailed pathways are shown below:



The electrodeposition cell sketch is shown in Fig. 1a. A schematic illustration of the formation of  $\alpha(\beta)$ -PbO<sub>2</sub> doped with Co<sub>3</sub>O<sub>4</sub> and CNTs porous composite materials is given in Fig. 1b, which includes the following four steps: mass transfer, absorption, deposition and growth.

### 2.2 Characterization of the composite materials

The phase structures of the composite materials were measured using a D/max2200 X-ray diffractometer (XRD, Cu K $\alpha$  radiation). The surface morphologies and chemical composition were tested using a Nova Nano-SEM450 field emission scanning electron microscope (FE-SEM) equipped with energy dispersive spectroscopy (EDS).

The anodic polarization, CV and Tafel curves were carried out using an electrochemical workstation (CHI760E) with a standard three-electrode system. In which, the composite materials were used as the working electrode and its effective area was 1 cm<sup>2</sup>. A saturated calomel electrode (SCE) was used as the reference electrode and the counter electrode was a stainless-steel plate. The reference electrode and the working electrode were linked by a Luggin capillary filled with agar and potassium chloride. In addition, the distance between the capillary and the working electrode was approximately 2*d* (*d* is the diameter of the capillary). The compositions of the tested simulated solution were 50 g L<sup>-1</sup> Zn<sup>2+</sup> and 150 g L<sup>-1</sup> H<sub>2</sub>SO<sub>4</sub>, and the temperature was maintained at 35 °C. For impedance measurements, a Solartron Analytical (ModulLab XM) was used.

## 3. Results and discussion

### 3.1 Structure and surface morphology of PbO<sub>2</sub> and its composite materials

The XRD patterns of PbO<sub>2</sub> (a), PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub> (b), PbO<sub>2</sub>-CNTs (c) and PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub>-CNTs (d) deposits are presented in Fig. 2.

It can be seen from Fig. 2 that the main diffraction peaks of  $\beta$ -PbO<sub>2</sub> appeared at 25.4° and 31.9°, and their corresponding crystal planes were (110) and (101), in accordance with the standard card (JCPDS no: 41-1492). The main diffraction peaks of  $\alpha$ -PbO<sub>2</sub> appeared at 28.6°, 36.2° and 49.0°, and their corresponding crystal planes were (110), (200) and (130), in accordance with the standard card (JCPDS no: 45-1416). Co<sub>3</sub>O<sub>4</sub> diffraction peaks were observed in the patterns of PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub> and PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub>-CNTs deposits, showing that some Co<sub>3</sub>O<sub>4</sub> particles from the electrolyte were co-deposited into the structures of  $\alpha(\beta)$ -PbO<sub>2</sub>. In particular, for the PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub> deposit, the co-deposition of Co<sub>3</sub>O<sub>4</sub> particles into the  $\alpha(\beta)$ -PbO<sub>2</sub> obviously promoted the crystallization of PbO<sub>2</sub> and made the diffraction intensity sharper at 25.4°, 31.9°. In addition, it can



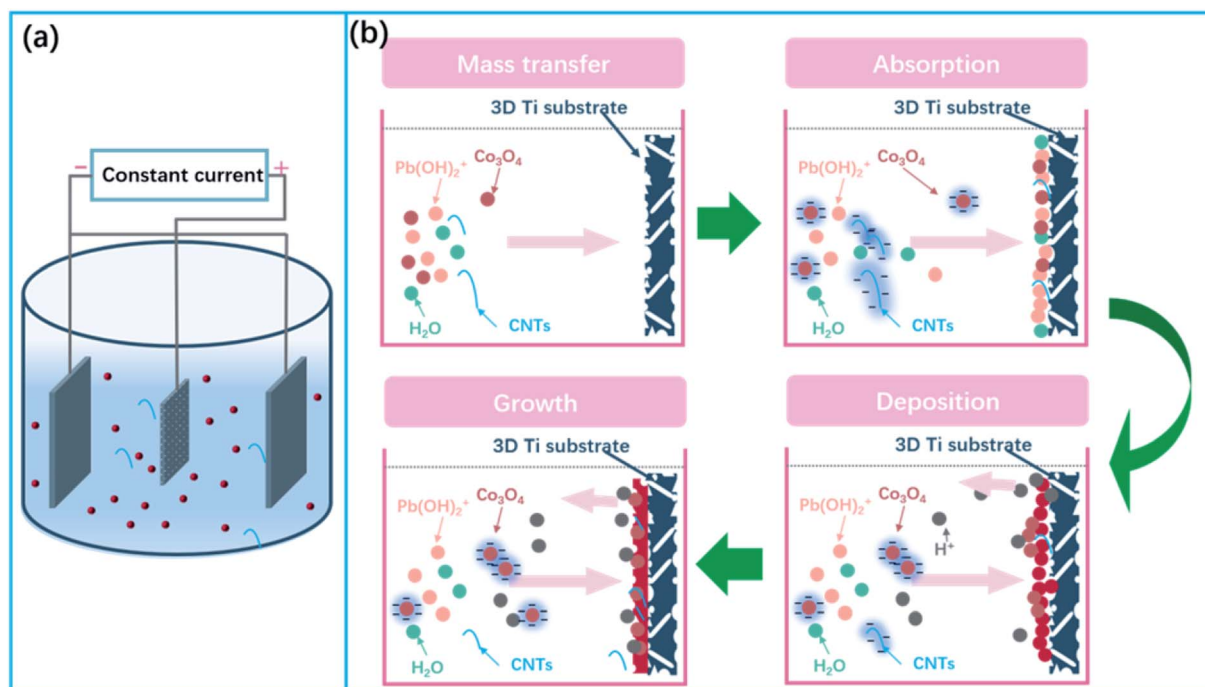


Fig. 1 (a) Sketch of the electrodeposition cell; (b) schematic illustration of the fabrication of composite materials.

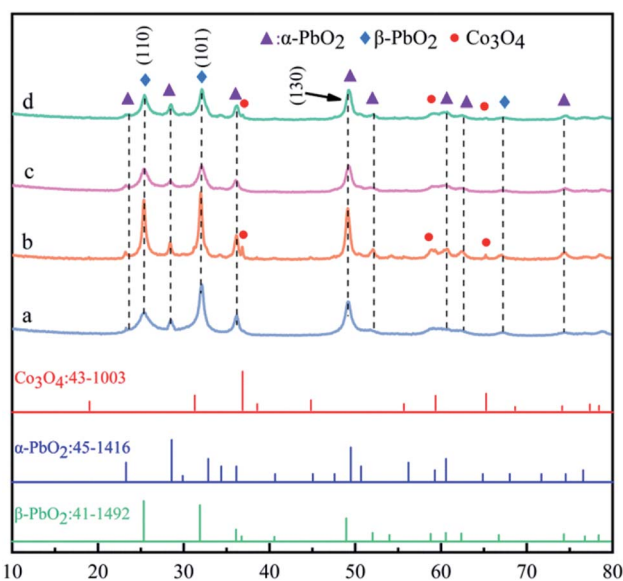


Fig. 2 XRD patterns of (a)  $\text{PbO}_2$ , (b)  $\text{PbO}_2\text{-Co}_3\text{O}_4$ , (c)  $\text{PbO}_2\text{-CNTs}$  and (d)  $\text{PbO}_2\text{-Co}_3\text{O}_4\text{-CNT}_5$  deposits.

be observed from Fig. 2c and d that the characteristic peaks of CNTs were not observed; this might be due to low content.<sup>22</sup>

The abovementioned research showed that  $\alpha\text{-PbO}_2$  and  $\beta\text{-PbO}_2$  deposits doped with  $\text{Co}_3\text{O}_4$  particles on the porous Ti substrates were obtained simultaneously from an electrolyte of  $\text{Pb}(\text{CH}_3\text{COO})_2\text{-NH}_2\text{SO}_3\text{H}$ ,  $\text{PbO}_2$  and its composite materials mainly consisted of the  $\alpha\text{-PbO}_2$  and  $\beta\text{-PbO}_2$  phases, and a small portion  $\text{Co}_3\text{O}_4$  particles. Whether CNTs were co-deposited into the  $\alpha(\beta)\text{-PbO}_2$  deposit cannot be judged according to XRD patterns only.

Fig. 3 shows the SEM images of the porous titanium substrate and the different composite materials, where Fig. 3a, b, c, d and e represent the porous titanium substrate, the deposits of  $\text{PbO}_2$ ,  $\text{PbO}_2\text{-Co}_3\text{O}_4$ ,  $\text{PbO}_2\text{-CNTs}$  and  $\text{PbO}_2\text{-Co}_3\text{O}_4\text{-CNTs}$ , respectively.

It can be observed from Fig. 3a that some irregular pores existed on the surface and inside of the Ti substrate. After  $\alpha(\beta)\text{-PbO}_2$  deposition for 60 min (Fig. 3b–e), these pores were still not completely filled up by deposited  $\text{PbO}_2$ . The  $\text{PbO}_2$  can deposit on the outside and the inside of the porous Ti substrate to make the deposit porous. The existence of pores can promote the formation of an embedded structure, making the combination between the  $\text{PbO}_2$  deposit and the substrate more compact. In addition, the pores can also help to eliminate the internal stress generated in the crystals.<sup>23</sup> Hence, it is very important to form a porous microstructure to meet the requirements for physical and electrochemical performance. In general, the pores can be gradually covered by  $\text{PbO}_2$  with increasing depositing time. Therefore, it is crucial to control the deposited time to obtain a porous microstructure. It also can be observed from Fig. 3b that the morphology of the deposit is a polygonal crystallite microstructure, which is different from the pure  $\alpha\text{-PbO}_2$  or  $\beta\text{-PbO}_2$ ; this might be caused by its composition of mixed phases of  $\alpha\text{-PbO}_2$  and  $\beta\text{-PbO}_2$ .

As for  $\text{PbO}_2\text{-Co}_3\text{O}_4$  (Fig. 3c),  $\text{PbO}_2\text{-CNTs}$  (Fig. 3d) and  $\text{PbO}_2\text{-Co}_3\text{O}_4\text{-CNTs}$  (Fig. 3e) deposits, the surfaces of these deposits are different from the  $\text{PbO}_2$  deposit (Fig. 3b). Apparently, the surfaces of these deposits are rougher as compared to the  $\text{PbO}_2$  deposit. From Fig. 3c–e, some other pores can clearly be observed, which might mean that the manner of nucleation and growth of  $\text{PbO}_2$  was changed.





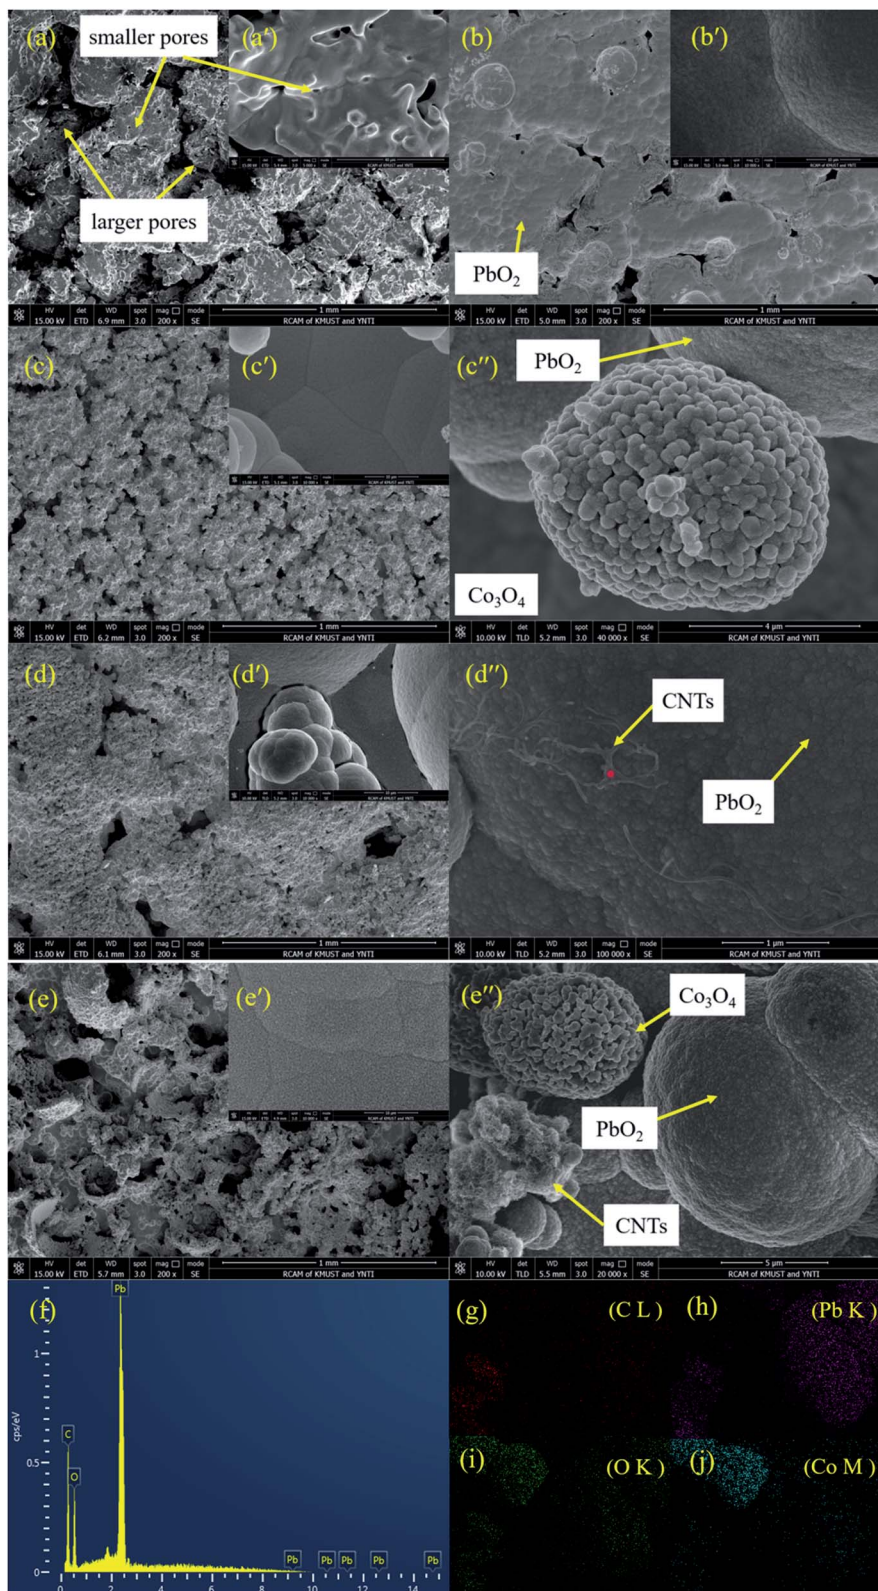


Fig. 3 SEM images of the deposits: (a) porous substrate; (b) 3D-Ti/PbO<sub>2</sub> deposit; (c) 3D-Ti/PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub> deposit; (d) 3D-Ti/PbO<sub>2</sub>-CNTs deposit; (e) 3D-Ti/PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub>-CNTs deposit. (f) EDS of selected points in (d''). (g–j) The element mapping results of zone (e'').

It can be observed from Fig. 3d'' that CNTs have been co-deposited and distributed uniformly in the PbO<sub>2</sub> deposit, which was also proven by EDS results (Fig. 3f). When SDS was

added to the Pb(CH<sub>3</sub>COO)<sub>2</sub>-NH<sub>2</sub>SO<sub>3</sub>H electrolyte, the negatively charged [CNTs-SDS]<sup>n-</sup> was probably formed and the aggregation of CNTs was decreased in the electrolyte. Moreover, [CNTs-



SDS]<sup>n-</sup> could migrate toward the anode surface in the electric field, promoting the co-deposition of CNTs with PbO<sub>2</sub>.<sup>24,25</sup> Similarly, Co<sub>3</sub>O<sub>4</sub> and CNTs were also simultaneously co-deposited into PbO<sub>2</sub> deposits (Fig. 3e and elements mapping Fig. 3g–j). Hence, it was confirmed that  $\alpha(\beta)$ -PbO<sub>2</sub> doped with Co<sub>3</sub>O<sub>4</sub> and CNTs porous composite materials were successfully fabricated.

In addition, the crystal grain sizes (*D*) of different deposits were calculated by Debye–Scherrer's eqn (5):

$$D = \frac{k\lambda}{\beta \cos \theta} \quad (5)$$

where  $\theta$  is the diffraction angle,  $\lambda$  is the X-ray wavelength and  $\beta$  is the full width at half-maximum. The results are displayed in Table S1† and Fig. 4.

As shown in Fig. 4a, the grain sizes at the (110), (101) and (130) crystal faces of different deposits, arranged from largest to smallest, are as follows: PbO<sub>2</sub>–Co<sub>3</sub>O<sub>4</sub>, PbO<sub>2</sub>–Co<sub>3</sub>O<sub>4</sub>–CNTs, PbO<sub>2</sub> and PbO<sub>2</sub>–CNTs. The PbO<sub>2</sub> deposit doped with single Co<sub>3</sub>O<sub>4</sub> showed the maximum crystal grain size at the (110), (101) and (130) crystal faces. This may be due to the formation of larger grains of Co<sub>3</sub>O<sub>4</sub> particles that were covered by PbO<sub>2</sub> grains. The PbO<sub>2</sub>–CNTs deposit displayed the minimum crystal grain sizes, revealing that CNTs could refine the crystal grains. This may be because CNTs with superior electrical conductivity improved the nucleation of PbO<sub>2</sub> when adsorbed on the surface of the substrate (Fig. 4b), and the growth rate of the PbO<sub>2</sub> grains decreased. The crystal grain sizes of PbO<sub>2</sub>–Co<sub>3</sub>O<sub>4</sub>–CNTs were slightly larger as compared to PbO<sub>2</sub>–CNTs, suggesting that the influence of CNTs on the growth of PbO<sub>2</sub> grains played a more important role during the co-depositing of PbO<sub>2</sub>, Co<sub>3</sub>O<sub>4</sub> and CNTs.

### 3.2 The electrocatalytic activity for OER characterizations

In zinc electrowinning, the sluggish kinetics of the OER determines the electric energy consumption. Hence, the OER electrocatalytic activity is a key factor in evaluating an anode material. To investigate the OER electrocatalytic activity of PbO<sub>2</sub>

and its composite materials, anode polarization technology was adopted at a scan rate of 10 mV s<sup>-1</sup> in a simulated zinc solution (50 g L<sup>-1</sup> Zn<sup>2+</sup>, 150 g L<sup>-1</sup> H<sub>2</sub>SO<sub>4</sub>); the results are presented in Fig. 5a. The electrocatalytic activity of the PbO<sub>2</sub> and its composite materials arranged from good to poor are as follows: 3D-Ti/PbO<sub>2</sub>–Co<sub>3</sub>O<sub>4</sub>–CNTs, 3D-Ti/PbO<sub>2</sub>–CNTs, 3D-Ti/PbO<sub>2</sub>–Co<sub>3</sub>O<sub>4</sub> and 3D-Ti/PbO<sub>2</sub>, according to the OER potential.

Fig. 5b presents the OER potential and overpotential of PbO<sub>2</sub> and its composite materials. The OER potential and overpotential of 3D-Ti/PbO<sub>2</sub>, 3D-Ti/PbO<sub>2</sub>–Co<sub>3</sub>O<sub>4</sub>, 3D-Ti/PbO<sub>2</sub>–CNTs and 3D-Ti/PbO<sub>2</sub>–Co<sub>3</sub>O<sub>4</sub>–CNTs, arranged from high to low, are as follows: 1.762 V, 1.624 V, 1.512 V, 1.424 V, and 0.7583 V, 0.6203 V, 0.5138 V, 0.4203 V, respectively, at a current density of 500 A cm<sup>-2</sup>. The OER potential and overpotential of the PbO<sub>2</sub> composite materials doped with Co<sub>3</sub>O<sub>4</sub> and CNTs were obviously lower as compared to 3D-Ti/PbO<sub>2</sub>, indicating that Co<sub>3</sub>O<sub>4</sub> and CNTs are beneficial for enhancing the OER electrocatalytic activity. Besides, the abovementioned potentials and overpotential were obviously lower than those of the Pb–0.76% Ag alloy with potential 1.870 V and overpotential 0.872 V.<sup>26</sup>

The inset in Fig. 5a is the Tafel linear fitting curves ( $\eta = a + b \log i$ ) for PbO<sub>2</sub> and its composite materials. The parameters of Tafel linear fitting are listed in Table 1 (linear fitting range: 300–600 A m<sup>-2</sup>).

$\eta$  is the OER overpotential,  $a$  is the intercept,  $b$  is the Tafel slope and  $i_0$  is the exchange current density. Among these parameters, the exchange current density ( $i_0$ ) as a primary driver is the most important factor for evaluating the electrocatalytic activity; a large  $i_0$  suggests that the OER occurs easily and with less power consumption. It can be seen from Table 1 that 3D-Ti/PbO<sub>2</sub>–Co<sub>3</sub>O<sub>4</sub>–CNTs showed the largest  $i_0$  value with  $2.055 \times 10^{-3}$ , representing the optimal electrochemical activity.

It can be concluded from the above research that 3D-Ti/PbO<sub>2</sub>–Co<sub>3</sub>O<sub>4</sub>–CNTs showed the optimal electrochemical activity. The reason may be that the second phase, such as Co<sub>3</sub>O<sub>4</sub> and CNTs, improved the electrocatalytic activity.

The spinel Co<sub>3</sub>O<sub>4</sub> consists of two kinds of Co ions (Fig. 6):<sup>27</sup> Co<sup>2+</sup> located in the tetrahedral site and two other Co<sup>3+</sup> ions in

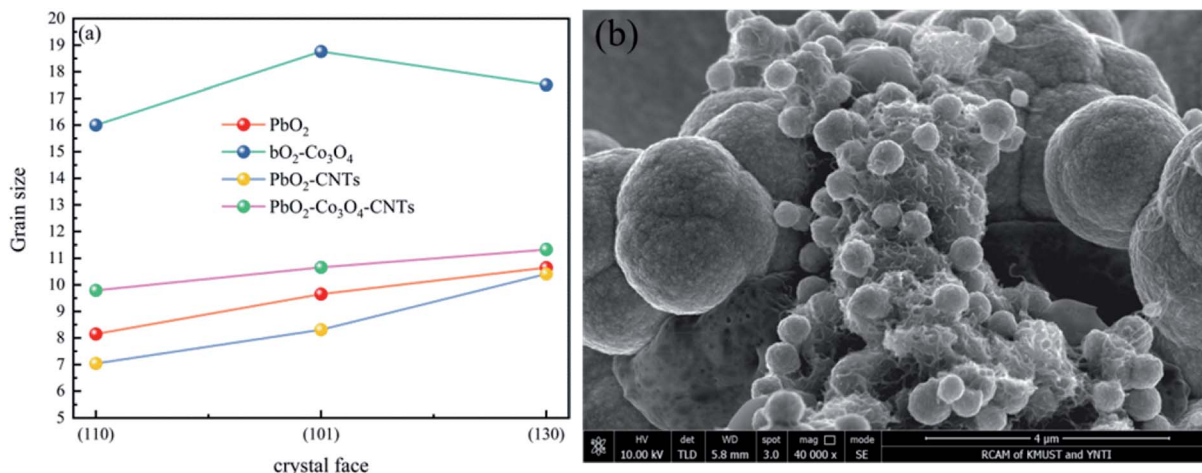


Fig. 4 (a) The grain size on different crystal faces of different deposits and (b) the nucleation of lead dioxide on the CNTs.






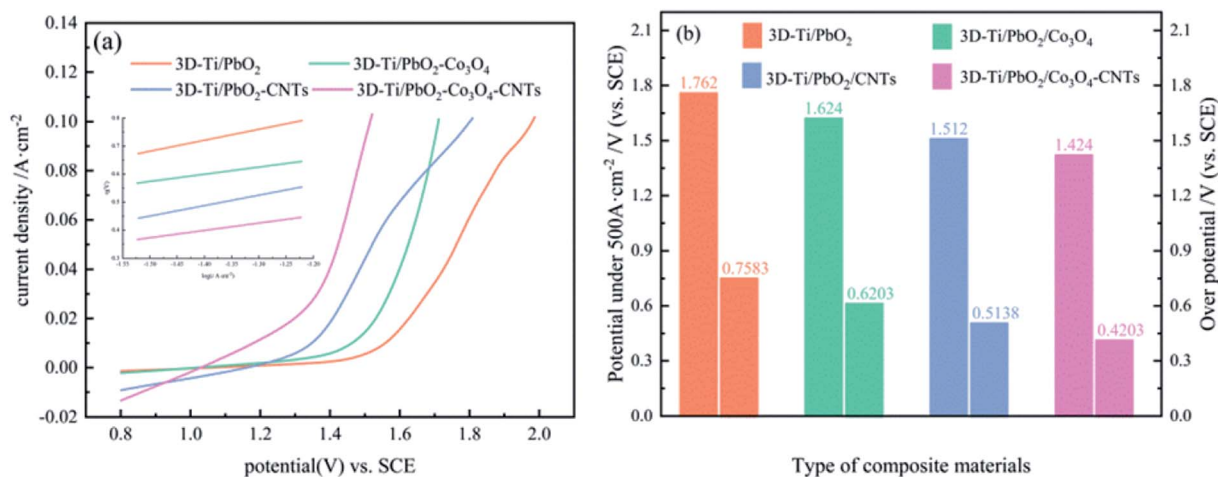


Fig. 5 (a) Anodic polarization curves of PbO<sub>2</sub> and its composite materials. (b) The potential and overpotential of PbO<sub>2</sub> and its composite materials at the current density of 500 A m<sup>-2</sup> in a simulated zinc solution.

Table 1 The oxygen evolution reaction kinetic factors of four types of materials

Material type	OER kinetic factors		
	<i>a</i>	<i>b</i> (V dec <sup>-1</sup> )	<i>i</i> <sub>0</sub>
3D-Ti-PbO <sub>2</sub>	1.2697	0.3922	5.789 × 10 <sup>-4</sup>
3D-Ti/PbO <sub>2</sub> -Co <sub>3</sub> O <sub>4</sub>	0.9589	0.2563	1.814 × 10 <sup>-4</sup>
3D-Ti/PbO <sub>2</sub> -CNTs	1.0105	0.3732	1.954 × 10 <sup>-3</sup>
3D-Ti/PbO <sub>2</sub> -Co <sub>3</sub> O <sub>4</sub> -CNTs	0.7043	0.2621	2.055 × 10 <sup>-3</sup>


the octahedral site.<sup>28</sup> The extraordinary structure may be related to its extra electrocatalytic activity. Besides, the transformation between Co<sup>2+</sup> and Co<sup>3+</sup> might correspond to the electrocatalytic activity. It has been reported that a small portion of Co<sub>3</sub>O<sub>4</sub> could turn into Co<sup>2+</sup> in aqueous solution at a higher potential, which is beneficial for the oxygen evolution. Once a few Co<sub>3</sub>O<sub>4</sub> formed Co<sup>2+</sup>, the redox couple of Co<sup>2+</sup> and Co<sup>3+</sup> is absorbed at the active sites of PbO<sub>2</sub>. This process can be described by eqn (6)–(9). The existence of these reactions reduced the oxygen potential.<sup>1,29–32</sup>



The superior electric conductivity of CNTs would help to improve the OER electrocatalytic activity, which has been demonstrated in a recent report.<sup>33</sup> When Co<sub>3</sub>O<sub>4</sub> and CNTs were doped into PbO<sub>2</sub>, a synergetic effect contributed to the OER electrocatalytic activity.<sup>34,35</sup>

Secondly, the second active phase may alter the kinetics, specifically, the rate determination step (rds) during the OER process.

In the electrowinning process of zinc, the anodic reaction can be ascribed to the eqn (10):



The detailed reaction pathways for OER on the active metal oxides electrode are described in Table 2:<sup>36</sup>

S indicates the active site on the metal oxide surface, S-OH<sub>ads</sub> and S-O<sub>ads</sub> represent adsorbed intermediate species and *b* is the Tafel slope. Among the 4 steps in Table 2, the rds is commonly associated with the Tafel slope (*b*) for the OER. For PbO<sub>2</sub>, the generation of the adsorbed intermediate S-O<sub>ads</sub> (11)

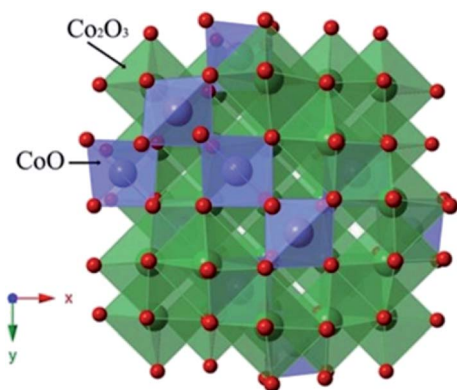


Fig. 6 The spinel structure of Co<sub>3</sub>O<sub>4</sub>.

Table 2 The reaction pathways for the OER in acidic medium

Step	<i>b</i> /V dec <sup>-1</sup>	—
S + H <sub>2</sub> O → S-OH <sub>ads</sub> + H <sup>+</sup> + e <sup>-</sup>	0.12	(11)
S-OH <sub>ads</sub> → S-O <sub>ads</sub> + H <sup>+</sup> + e <sup>-</sup>	0.04	(12a)
2S-OH <sub>ads</sub> → S-O <sub>ads</sub> + S + H <sub>2</sub> O	0.03	(12b)
2S-O <sub>ads</sub> → S + O <sub>2</sub>	0.015	(13)





was supposed to be rds when  $b$  is equal to or greater than  $0.12 \text{ V dec}^{-1}$ .<sup>36</sup> The  $b$  values of  $\text{PbO}_2$  and its composite materials ranged from 0.2563 to  $0.3922 \text{ V dec}^{-1}$ , and were larger than  $0.12 \text{ V dec}^{-1}$ ; hence, step (11) was rds in the present research. Consequently, the outstanding electrocatalytic activity of the  $\text{PbO}_2$  composite materials doped with  $\text{Co}_3\text{O}_4$  and CNTs may be attributed to more  $\text{S-O}_{\text{ads}}$  when  $\text{Co}_3\text{O}_4$  and CNTs were doped into  $\text{PbO}_2$ .

Thirdly, the electrocatalytic activity is affected by the active surface area; a large active surface area can provide more active sites that are beneficial to improve the electrochemical efficiency. It is known that the active surface area is related to the voltammetric charge ( $q^*$ ), which was usually measured by CV technology.<sup>15,35</sup>

It has been reported that the voltammetric charge ( $q^*$ ) consists of two parts: the outer voltammetric charge ( $q_o^*$ ) and the inner voltammetric charge ( $q_i^*$ ).  $q_o^*$  can be calculated by the following equation:

$$q^* = q_o^* + kv^{-1/2} \quad (14)$$

where  $k$  is a constant, and  $q_o^*$  can be obtained by the extrapolation method when the  $v = \infty$ .

$q_T^*$  can be obtained by plotting  $q^*$  versus the square root of the scan rate as expressed by the following equation:

$$(q^*)^{-1} = (q_T^*)^{-1} + k'v^{1/2} \quad (15)$$

where  $k'$  is also a constant, and  $q_T^*$  can be calculated when  $v = 0$ .

$q_i^*$  can be acquired from the following equation:

$$q_T^* = q_o^* + q_i^* \quad (16)$$

The cyclic voltammogram curves of  $\text{PbO}_2$  and its composite materials in an aqueous electrolyte containing  $50 \text{ g L}^{-1} \text{ Zn}^{2+}$  and  $150 \text{ g L}^{-1} \text{ H}_2\text{SO}_4$ , are shown in Fig. 7a; the plots of  $q^*$  against the reciprocal square root of potential scan rate ( $v^{-1/2}$ ) are depicted in Fig. 7b; the linear fitting of  $(q^*)^{-1}$  versus  $v^{-1/2}$  is displayed in Fig. 7c and  $q_T^*$ ,  $q_o^*$ ,  $q_i^*$  and  $q_i^*/q_T^*$  for  $\text{PbO}_2$  and its materials are summarized in Table S2† and Fig. 7d.

Fig. 7b and c depict a good linear relationship between  $q^*$  and  $v^{-1/2}$ , and  $(q^*)^{-1}$  and  $v^{1/2}$ , respectively. It can be seen from Table S2† that the  $q_T^*$  values of 3D-Ti/ $\text{PbO}_2$ - $\text{Co}_3\text{O}_4$ -CNTs, 3D-Ti/ $\text{PbO}_2$ -CNTs, 3D-Ti/ $\text{PbO}_2$ - $\text{Co}_3\text{O}_4$  and 3D-Ti/ $\text{PbO}_2$  were 39.04, 5.388, 2.311 and 0.26, so the total voltammetric charge was

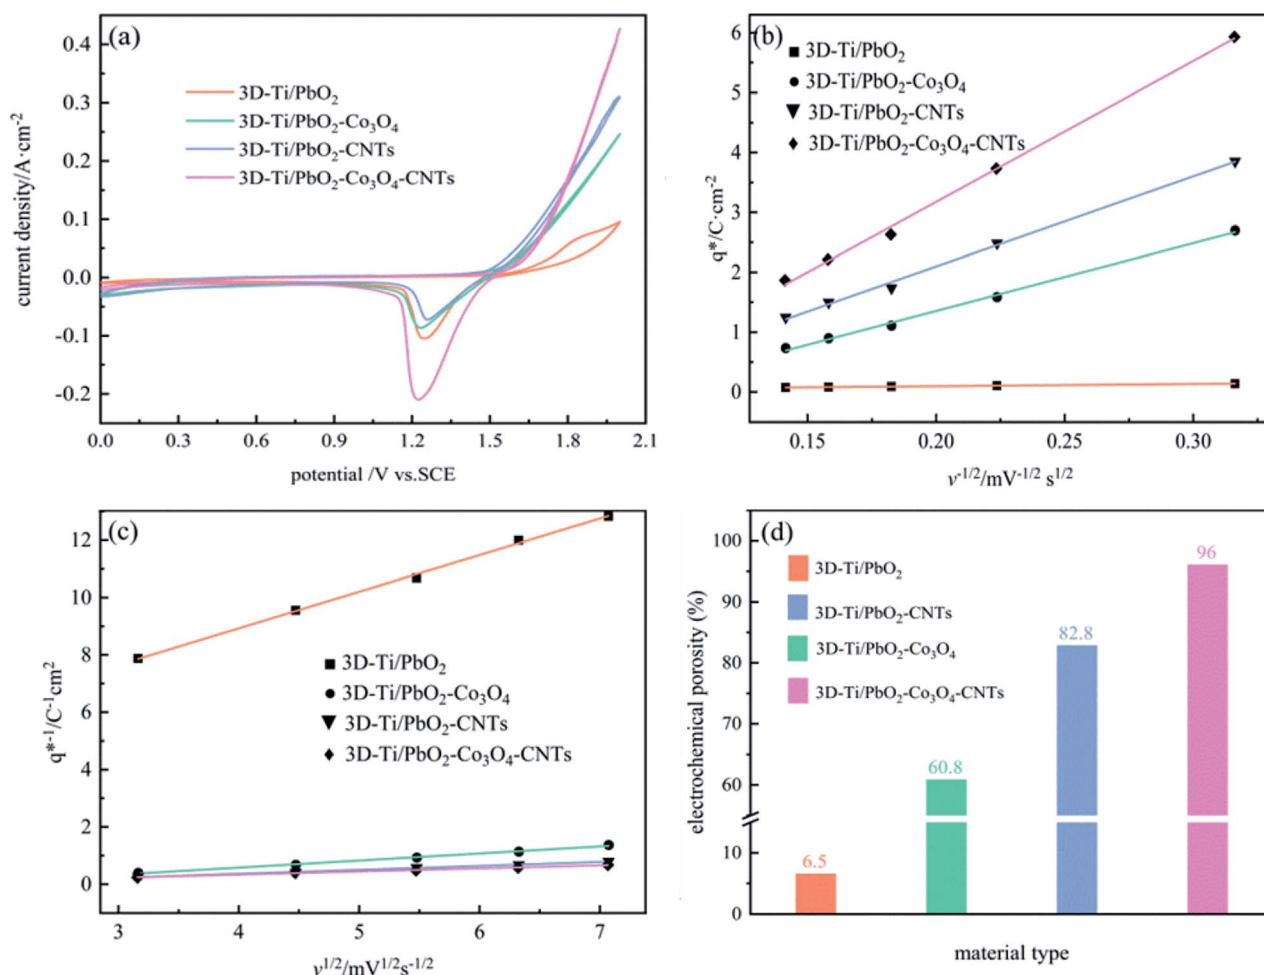


Fig. 7 (a) Cyclic voltammogram curves of  $\text{PbO}_2$  and its composite materials; (b) relationship of  $q^*$  versus  $v^{-1/2}$ ; (c) relationship of  $(q^*)^{-1}$  versus  $v^{1/2}$ ; (d) diagram showing electrochemical porosity.



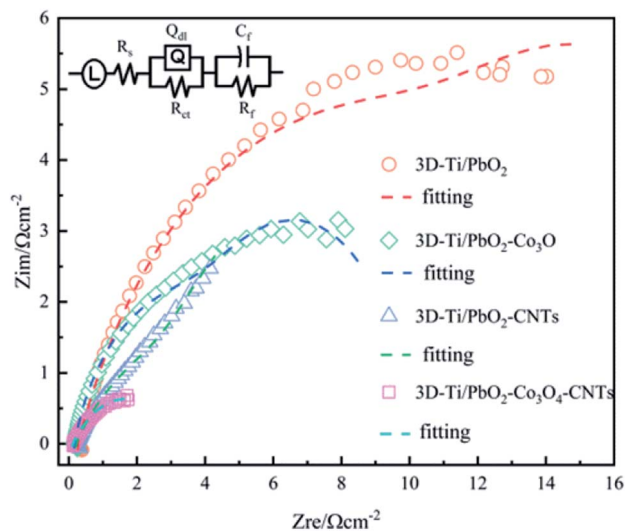


Fig. 8 EIS plots for 3D-Ti/PbO<sub>2</sub>, 3D-Ti/PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub>, 3D-Ti/PbO<sub>2</sub>-CNTs and 3D-Ti/PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub>-CNTs.

apparently increased when Co<sub>3</sub>O<sub>4</sub> and CNTs were doped into PbO<sub>2</sub>. Besides, it can be observed from Fig. 7d that the electrochemical porosity is arranged from large to small as follows: 96.5%, 82.8%, 60.8% and 6.5% for 3D-Ti/PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub>-CNTs, 3D-Ti/PbO<sub>2</sub>-CNTs, 3D-Ti/PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub> and 3D-Ti/PbO<sub>2</sub>.

The doping of Co<sub>3</sub>O<sub>4</sub> and CNTs into PbO<sub>2</sub> and the porous structure increased the active surface area, and the 3D-Ti/PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub>-CNTs exhibited the best electrocatalytic activity.

Additionally, PbO<sub>2</sub> and its composite materials were tested by EIS technology to evaluate their electrocatalytic activity, the Nyquist plots under a constant potential of 1.5 V (vs. SCE) are shown in Fig. 8.

It is clear that 3D-Ti/PbO<sub>2</sub> showed the highest impedance, followed by 3D-Ti/PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub>, 3D-Ti/PbO<sub>2</sub>-CNTs and 3D-Ti/PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub>-CNTs. The EIS was investigated by the LR(QR) (CR) equivalent circuit (inset in Fig. 8), which was adopted from a report that also studied the DSA anodes. *L* can be ascribed to the electrochemical system,<sup>37</sup> *R<sub>s</sub>* is the resistance of the solution, *R<sub>ct</sub>* is the polarization (or charge transfer) resistance for oxygen evolution and *Q<sub>dl</sub>* is a constant phase element related to the double-layer capacitance at the Ti |deposited composite| electrolyte. The combination of *R<sub>ct</sub>* and *Q<sub>dl</sub>* indicates the behavior of the interface between the deposited composite and electrolyte, which can be calculated by eqn (17). The combination of *C<sub>f</sub>* and *R<sub>f</sub>* (*C<sub>f</sub>R<sub>f</sub>*) determines the properties of the oxide layer.<sup>38,39</sup>

$$Z_{CPE} = [Q(j\omega)^n]^{-1} \quad (17)$$

Here, *j* is equal to  $\sqrt{-1}$ ,  $\omega$  is the angular velocity defined  $2\pi f$  with being frequency, *Q* is the constant phase element, and *n* is an empirical constant between 0 and 1. When *n* = 1, the CPE is a pure capacitance. The effective capacitance *C* can be calculated by eqn (18):

$$C = R^{\frac{1-n}{n}} Q^{\frac{1}{n}} \quad (18)$$

where *R* is the resistance.<sup>40–42</sup>

The circuit parameters for all prepared materials were calculated and are listed in Table 3. The *R<sub>s</sub>* ranged from 0.123 to 0.284. The slight difference can be ascribed to the oxygen bubble on the surface, which blocked the interface of the electrode and electrolyte. The double-layer capacitance (*C<sub>dl</sub>*) of both doped Co<sub>3</sub>O<sub>4</sub> and CNTs was about 15 times higher than that without doped particles, which showed a higher electrochemically active surface area (ECSA).<sup>43</sup> Besides, 3D-Ti/PbO<sub>2</sub>-Co<sub>3</sub>O<sub>4</sub>-CNTs composite materials showed the lowest *R<sub>ct</sub>* value, which was only about one fourth lower than that of 3D-Ti/PbO<sub>2</sub>, illustrating the higher electrocatalytic activity for the OER.

It is known that CNTs are metallic with high conductivity of  $\sim 100 \text{ S m}^{-1}$  (about 2-fold that of PbO<sub>2</sub> ( $\sim 59 \text{ S m}^{-1}$ )).<sup>44,45</sup> The addition of CNTs could bridge the PbO<sub>2</sub> and Ti substrate, and result in low *R<sub>ct</sub>* (shown in Table 3). Xu *et al.* also found that CNTs could support a long-term electron exchange between the Pt and Pd without direct atomic contact.<sup>46</sup>

For comparison, the OER performances of some electrodes have been listed in Table S3† and Fig. 9.

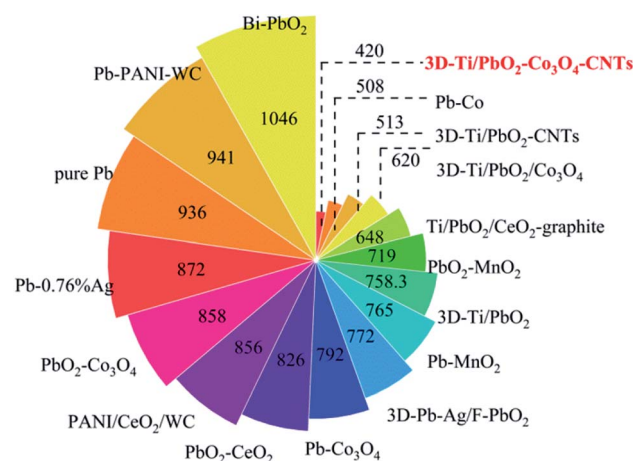


Fig. 9 The overpotential of different composite materials at 500 A cm<sup>-2</sup>.

Table 3 Parameters obtained from the EIS data for the OER at four types of composite materials

Material type	<i>L</i> /μH	<i>R<sub>s</sub></i> (Ω <sup>-1</sup> cm <sup>-2</sup> )	<i>R<sub>ct</sub></i> (Ω <sup>-1</sup> cm <sup>-2</sup> )	<i>n</i>	<i>Q<sub>dl</sub></i> (Ω <sup>-1</sup> cm <sup>-2</sup> s <sup><i>n</i></sup> )	<i>C<sub>dl</sub></i> (F cm <sup>-2</sup> )	<i>R<sub>f</sub></i> (Ω <sup>-1</sup> cm <sup>-2</sup> )	<i>Q<sub>f</sub></i> (Ω <sup>-1</sup> cm <sup>-2</sup> s <sup><i>n</i></sup> )
3D-Ti/PbO <sub>2</sub>	0.128	0.284	13.5	0.686	0.0218	0.4115	7.455	0.280
3D-Ti/PbO <sub>2</sub> -Co <sub>3</sub> O <sub>4</sub>	0.085	0.186	4.73	0.762	0.762	1.5369	5.033	0.173
3D-Ti/PbO <sub>2</sub> -CNTs	0.070	0.231	4.56	0.754	0.120	0.3897	5.232	0.754
3D-Ti/PbO <sub>2</sub> -Co <sub>3</sub> O <sub>4</sub> -CNTs	0.096	0.123	3.11	0.496	0.38	6.3250	0.00562	0.00566





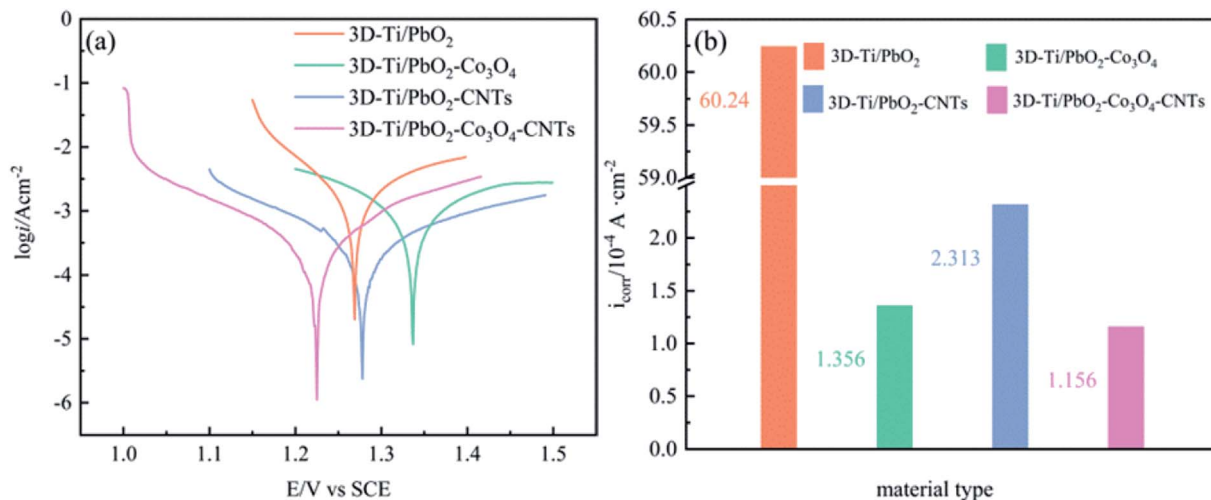


Fig. 10 (a) Tafel polarization curves of  $\text{PbO}_2$  and its composite materials (scan rate:  $1 \text{ mV s}^{-1}$ ), (b) self-corrosion current density ( $i_{\text{corr}}$ ) of different composite materials in the simulated zinc solution.

As can be seen from Fig. 9, 3D-Ti/ $\text{PbO}_2$ - $\text{Co}_3\text{O}_4$ , 3D-Ti/ $\text{PbO}_2$ -CNTs and 3D-Ti/ $\text{PbO}_2$ - $\text{Co}_3\text{O}_4$ -CNTs exhibited the best OER electrocatalytic activity. The outstanding electrocatalytic activity of 3D-Ti/ $\text{PbO}_2$ - $\text{Co}_3\text{O}_4$ -CNTs can be attributed to the porous structure (Fig. 3), small crystal grain sizes (Fig. 5a) and the second phases such as  $\text{Co}_3\text{O}_4$  and CNTs. The porous structure not only provided more active surface area but also gave more channels for removing oxygen generated in the reaction. The small grain size offered more active sites. In addition,  $\text{Co}_3\text{O}_4$  with excellent catalytic activity and CNTs with outstanding electric conductivity improved the electrocatalytic activity when doped into  $\text{PbO}_2$  deposits. Therefore, 3D-Ti/ $\text{PbO}_2$ - $\text{Co}_3\text{O}_4$ -CNTs composite materials showed excellent electrocatalytic activity for the OER.

### 3.3 Corrosion resistance characterization

The high corrosion resistance of electrode materials is necessary to maintain long service life; hence, in order to investigate the corrosion resistance, the Tafel technology was used at a scan rate of  $1 \text{ mV s}^{-1}$  in a simulated zinc solution ( $50 \text{ g L}^{-1} \text{ Zn}^{2+}$ ,  $150 \text{ g L}^{-1} \text{ H}_2\text{SO}_4$ ). The results are shown in Fig. 10, and the corrosion currents and corrosion potentials are listed in Table S4.†

The value of  $E_{\text{corr}}$  reveals the self-corrosion capacity of the material without external power being supplied, and  $i_{\text{corr}}$  indicates the corrosion rate at a certain potential. As shown in Fig. 10b, the  $i_{\text{corr}}$  of 3D-Ti/ $\text{PbO}_2$ , 3D-Ti/ $\text{PbO}_2$ - $\text{Co}_3\text{O}_4$ , 3D-Ti/ $\text{PbO}_2$ -CNTs and 3D-Ti/ $\text{PbO}_2$ - $\text{Co}_3\text{O}_4$ -CNTs were  $6.024 \times 10^{-3}$ ,  $1.356 \times 10^{-4}$ ,  $2.314 \times 10^{-4}$  and  $1.156 \times 10^{-4} \text{ (A cm}^{-2}\text{)}$ , respectively. The  $i_{\text{corr}}$  of doped composite materials is lower by nearly an order of magnitude as compared to that of the Pb-1% Ag alloy ( $5.17 \times 10^{-3} \text{ A cm}^{-2}$ ).<sup>47</sup> It can be concluded that the doped composite materials presented better corrosion resistance in the simulated zinc solution ( $50 \text{ g L}^{-1} \text{ Zn}^{2+}$ ,  $150 \text{ g L}^{-1} \text{ H}_2\text{SO}_4$ ) at  $35^\circ\text{C}$ .

## 4. Conclusion

In summary, a  $\text{PbO}_2$  composite material doped with  $\text{Co}_3\text{O}_4$  and CNTs on a porous Ti substrate was prepared *via* a one-step

electrochemical deposition, which involved the  $\beta$ - $\text{PbO}_2$  phase, a small portion of the  $\alpha$ - $\text{PbO}_2$  phase,  $\text{Co}_3\text{O}_4$  and CNTs. The 3D-Ti/ $\text{PbO}_2$ - $\text{Co}_3\text{O}_4$ -CNTs composite material exhibited a porous structure with the highest electrochemical porosity of 96%, large electrochemical surface area of  $6.325 \text{ (F cm}^{-2}\text{)}$  and the lowest charge transfer resistance of  $3.11 \text{ ohm cm}^2$  in comparison to other electrodes. Compared with the Pb-0.76 wt% Ag alloy, the overpotential of the oxygen evolution was decreased by about 452 mV under the current density of  $500 \text{ A m}^{-2}$  in the simulated zinc electro-winning solution, displaying outstanding electrocatalytic activity. Furthermore, it showed the lowest self-corrosion current density, displaying good corrosion resistance.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

Authors gratefully acknowledge the financial support of the Natural Science Foundation of China (Project No. 51874154, 51564029), the Key Project of Yunnan Province Science and Technology Plan of China (Project No. 2014FA024); the Specialized Research Fund for the Doctoral Program of the Ministry of Education of China (Project No. 20125314110011) and Analysis and Measurement Research Fund (2017M20172128008) of Kunming University of Science and Technology.

## References

- M. Clancy, C. J. Bettles, A. Stuart and N. Birbilis, *Hydrometallurgy*, 2013, **131**–132, 144–157.
- X. Zhong, F. Chen, H. Nie, R. Wang and Z. Xu, *Hydrometallurgy*, 2019, **190**, 105188.
- X. Li, D. Pletcher and F. C. Walsh, *Chem. Soc. Rev.*, 2011, **40**, 3879–3894.



- 4 J. Zhao, C. Zhu, J. Lu, C. Hu, S. Peng and T. Chen, *Electrochim. Acta*, 2014, **118**, 169–175.
- 5 J. Aromaa and O. Forsén, *Electrochim. Acta*, 2006, **51**, 6104–6110.
- 6 A. T. Marshall and R. G. Haverkamp, *J. Mater. Sci.*, 2011, **47**, 1135–1141.
- 7 M. Zahedi, K. Jafarzadeh, M. Mirjani and H. M. Abbasi, *Ionics*, 2017, **24**, 451–458.
- 8 R. Ma, S. Cheng, X. Zhang, S. Li, Z. Liu and X. Li, *Hydrometallurgy*, 2016, **159**, 6–11.
- 9 W. Zhao, J. Xing, D. Chen and J. Shen, *J. Adv. Oxid. Technol.*, 2017, **20**, 20160181.
- 10 N. Comisso, S. Cattarin, P. Guerriero, L. Mattarozzi, M. Musiani and E. Verlato, *Electrochem. Commun.*, 2015, **60**, 144–147.
- 11 N. Comisso, S. Cattarin, P. Guerriero, L. Mattarozzi, M. Musiani and E. Verlato, *Electrochim. Acta*, 2016, **200**, 259–267.
- 12 N. Comisso, S. Cattarin, P. Guerriero, L. Mattarozzi, M. Musiani and E. Verlato, *Electrochem. Commun.*, 2016, **73**, 59–62.
- 13 N. Comisso, L. Armelao, S. Cattarin, P. Guerriero, L. Mattarozzi, M. Musiani, M. Rancan, L. Vázquez-Gómez and E. Verlato, *Electrochim. Acta*, 2017, **253**, 11–20.
- 14 N. Comisso, L. Armelao, S. Cattarin, P. Guerriero, L. Mattarozzi, M. Musiani, M. Rancan, L. Vázquez-Gómez and E. Verlato, *Electrochim. Acta*, 2018, **273**, 454–461.
- 15 W. Zhang, H. Kong, H. Lin, H. Lu, W. Huang, J. Yin, Z. Lin and J. Bao, *J. Alloys Compd.*, 2015, **650**, 705–711.
- 16 Y. He, W. Huang, R. Chen, W. Zhang, H. Lin and H. Li, *Sep. Purif. Technol.*, 2015, **156**, 124–131.
- 17 Y. He, W. Huang, R. Chen, W. Zhang and H. Lin, *Sep. Purif. Technol.*, 2015, **149**, 124–131.
- 18 J. Xing, D. Chen, W. Zhao, X. Peng, Z. Bai, W. Zhang and X. Zhao, *RSC Adv.*, 2015, **5**, 53504–53513.
- 19 S. Asim, Y. Zhu, M. Rana, J. Yin, M. W. Shah, Y. Li and C. Wang, *Chemosphere*, 2017, **169**, 651–659.
- 20 G. A. Sadakov, E. K. Burygina, A. A. Mazin and N. M. Pokhomov, *Chem. Informationsdienst*, 1978, **9**, DOI: 10.1002/chin.197832040.
- 21 J. Jiang, Y. Li, J. Liu, X. Huang, C. Yuan and X. W. Lou, *Adv. Mater.*, 2012, **24**, 5166–5180.
- 22 Z. Xu, H. Liu, J. Niu, Y. Zhou, C. Wang and Y. Wang, *J. Hazard. Mater.*, 2017, **327**, 144–152.
- 23 B. Chen, S. Wang, J. Liu, H. Huang, C. Dong, Y. He, W. Yan, Z. Guo, R. Xu and H. Yang, *Corros. Sci.*, 2018, **144**, 136–144.
- 24 R. Amadelli, L. Samiolo, A. B. Velichenko, V. A. Knysh, T. V. Luk'yanenko and F. I. Danilov, *Electrochim. Acta*, 2009, **54**, 5239–5245.
- 25 X. Duan, F. Ma, Z. Yuan, L. Chang and X. Jin, *J. Electroanal. Chem.*, 2012, **677–680**, 90–100.
- 26 I. Ivanov, Y. Stefanov, M. Petrova, Ts. Dobrev and J. P. Demaerel, *Hydrometallurgy*, 2000, **57**, 125–139.
- 27 M. Liang, M. Zhao, H. Wang, F. Wang and X. Song, *Journal of Energy Storage*, 2018, **17**, 311–317.
- 28 Y. Wang, S. F. Hung, H. Y. Chen, T. S. Chan, H. M. Chen and B. Liu, *J. Am. Chem. Soc.*, 2016, **138**, 36–39.
- 29 N. Ortiz Peña, D. Ihiawakrim, M. Han, B. Lassalle-Kaiser, S. Carencio, C. Sanchez, C. Laberty-Robert, D. Portehault and O. Ersen, *ACS Nano*, 2019, **13**, 11372–11381.
- 30 M. Favaro, J. Yang, S. Nappini, E. Magnano, F. M. Toma, E. J. Crumlin, J. Yano and I. D. Sharp, *J. Am. Chem. Soc.*, 2017, **139**, 8960–8970.
- 31 J. B. Gerken, J. G. Mcalpin, J. Y. C. Chen, M. L. Rigsby, W. H. Casey, R. D. Britt and S. S. Stahl, *J. Am. Chem. Soc.*, 2011, **133**, 14431–14442.
- 32 J. A. Koza, Z. He, A. S. Miller and J. A. Switzer, *Chem. Mater.*, 2012, **24**, 3567–3573.
- 33 I. S. Filimonenkov, G. A. Tsirlina and E. R. Savinova, *Electrochim. Acta*, 2019, **319**, 227–236.
- 34 Y. Cheng and S. P. Jiang, *Prog. Nat. Sci.: Mater. Int.*, 2015, **25**, 545–553.
- 35 Y. Dan, H. Lu, X. Liu, H. Lin and J. Zhao, *Int. J. Hydrogen Energy*, 2011, **36**, 1949–1954.
- 36 Y. Lai, Y. Li, L. Jiang, W. Xu, X. Lv, J. Li and Y. Liu, *J. Electroanal. Chem.*, 2012, **671**, 16–23.
- 37 J. M. Hu, H. M. Meng, J. Q. Zhang and C. N. Cao, *Corros. Sci.*, 2002, **44**, 1655–1668.
- 38 J. M. Hu, J. Q. Zhang and C. N. Cao, *Int. J. Hydrogen Energy*, 2004, **29**, 791–797.
- 39 S. Palmas, A. M. Polcaro, F. Ferrara, J. Rodriguez Ruiz, F. Delogu, C. Bonatto-Minella and G. Mulas, *J. Appl. Electrochem.*, 2008, **38**, 907–913.
- 40 A. Qayoom Mugheri, U. Aftab, M. Ishaq Abro, S. R. Chaudhry, L. Amaral and Z. H. Ibutoto, *Electrochim. Acta*, 2019, **306**, 9–17.
- 41 G. J. Brug and A. M. van den Eeden, *J. Electroanal. Chem.*, 1984, **176**, 275.
- 42 C. M. Gore, J. O. White, E. D. Wachsman and V. Thangadurai, *J. Mater. Chem. A*, 2014, **2**, 2363–2373.
- 43 C. C. L. Mccrory, S. Jung, I. M. Ferrer, S. M. Chatman, J. C. Peters and T. F. Jaramillo, *J. Am. Chem. Soc.*, 2015, **137**, 4347–4357.
- 44 W. Mindt, *J. Electrochem. Soc.*, 1969, **116**, 1076–1080.
- 45 J. Yang, Q. F. Shen, D. c. Zhai and Y. Gu, *J. Appl. Electrochem.*, 2019, **49**, 67–77.
- 46 F. Xu, Q. Lu, L. Ye and S. C. E. Tsang, *Chem. Commun.*, 2017, **53**, 7653–7656.
- 47 S. He, R. Xu, J. Wang, S. Han and B. Chen, *J. Wuhan Univ. Technol., Mater. Sci. Ed.*, 2016, **31**, 811–817.

