


 Cite this: *RSC Adv.*, 2020, 10, 524

# Nano-zirconia supported by graphitic carbon nitride for enhanced visible light photocatalytic activity

 Xiaojian Bi, Sirong Yu, Enyang Liu, \* Xiaoli Yin, Yan Zhao and Wei Xiong

Graphitic carbon nitride (g-C<sub>3</sub>N<sub>4</sub>) was prepared by high-temperature calcination of urea. A mixture of g-C<sub>3</sub>N<sub>4</sub> and nano-ZrO<sub>2</sub> precursor was directly calcined to prepare g-C<sub>3</sub>N<sub>4</sub>/ZrO<sub>2</sub> hybrid photocatalysts. The photocatalytic properties of the sample were characterized by degradation of rhodamine B (RhB) under visible light. The g-C<sub>3</sub>N<sub>4</sub>/ZrO<sub>2</sub> hybrid photocatalysts have better degradation performance than the pure g-C<sub>3</sub>N<sub>4</sub> and ZrO<sub>2</sub>. The prepared catalysts were characterized by various techniques including X-ray diffraction (XRD), scanning electron microscopy (SEM), transmission electron microscopy (TEM), UV-vis diffuse reflectance spectroscopy (DRS), Fourier transform infrared spectroscopy (FT-IR), and photoluminescence spectroscopy (PL) and electrochemical tests. The reasons for the improvement of catalytic activity were investigated from the aspects of crystal structure, surface morphology and photoelectric properties, and the catalytic mechanism were studied. The results show that the ZrO<sub>2</sub> nanoparticles were coated with g-C<sub>3</sub>N<sub>4</sub> to form a heterostructure. Compared with the pure g-C<sub>3</sub>N<sub>4</sub> and ZrO<sub>2</sub>, the g-C<sub>3</sub>N<sub>4</sub>/ZrO<sub>2</sub> hybrids reduce the charge transfer resistance and inhibit the recombination of electron–holes well. In addition, it affects the band structure and improves the absorption of visible-light. At the same time, the study found that the main active species in the catalytic process were h<sup>+</sup> and ·O<sub>2</sub><sup>-</sup>.

 Received 18th October 2019  
 Accepted 17th December 2019

DOI: 10.1039/c9ra08540h

[rsc.li/rsc-advances](http://rsc.li/rsc-advances)

## 1. Introduction

With the development of the economy, the problem of environmental pollution has become more and more prominent, so increasingly scientific research workers are committed to the treatment of environmental pollution.<sup>1,2</sup> In recent years, the use of solar energy for photolysis of water to produce hydrogen<sup>3–5</sup> and photocatalytic degradation of pollutants<sup>6–8</sup> has attracted extensive attention. A large number of semiconductor catalysts have been extensively studied, such as TiO<sub>2</sub>, ZnO, CeO<sub>2</sub> and WO<sub>3</sub>.<sup>9–12</sup> However, their forbidden band widths are too large, so they can only be excited under ultraviolet light, and the utilization rate of solar energy is not more than 4%.<sup>13</sup> In these semiconductor photocatalysts, the conduction band potential of ZrO<sub>2</sub> is about –1.0 eV, which is much lower than some semiconductors such as TiO<sub>2</sub> (–0.12 eV) and CeO<sub>2</sub> (–0.34 eV).<sup>12</sup> Few semiconductors contain such negative CB that can be used to sensitize ZrO<sub>2</sub>.

Senthil, Wang and Zhao reported a semiconductor photocatalyst, graphitic carbon nitride (g-C<sub>3</sub>N<sub>4</sub>), which is highly stable and low price. It is highly efficient in catalyzing hydrogen production and degrading organic pollutants under visible light.<sup>14–16</sup> It can be obtained by roasting inexpensive raw

materials, such as urea, thiourea and melamine.<sup>17–19</sup> The forbidden band width of g-C<sub>3</sub>N<sub>4</sub> is 2.7 eV, which is not only excited by visible light, but also has high solar energy utilization. In addition, g-C<sub>3</sub>N<sub>4</sub> is a layered structure, and there is a gap between layers, so the theoretical specific surface area should be large.<sup>20</sup> However, in actual performance studies, g-C<sub>3</sub>N<sub>4</sub> was found to exhibit significant defects, and its photogenerated carriers have extremely short lifetimes and are very easy to recombine. In order to improve its photocatalytic activity, various methods such as doping, noble metal loading and construction of heterojunctions have been researched.<sup>21–28</sup> Building a heterojunction is considered the most effective way. Wang *et al.* synthesized Cd<sub>0.5</sub>Zn<sub>0.5</sub>S/g-C<sub>3</sub>N<sub>4</sub> composite photocatalyst by two-step solvothermal method. The results showed that the photocatalytic performance of g-C<sub>3</sub>N<sub>4</sub> was greatly improved by the loading of Cd<sub>0.5</sub>Zn<sub>0.5</sub>S.<sup>29</sup> Lv *et al.* reported a g-C<sub>3</sub>N<sub>4</sub>/BiOBr photocatalyst which greatly reduced the recombination rate of electron–hole pairs, thereby effectively improving its catalytic activity.<sup>30</sup> However, the preparation of g-C<sub>3</sub>N<sub>4</sub>/ZrO<sub>2</sub> has rarely been reported. Since the conduction band potential of g-C<sub>3</sub>N<sub>4</sub> is –1.2 eV, ZrO<sub>2</sub> can be sensitized to increase its photocatalytic activity, it will be a very promising research direction.

In this paper, nano-ZrO<sub>2</sub> with an average particle size of 15.4 nm was prepared by precipitation method. The g-C<sub>3</sub>N<sub>4</sub>/ZrO<sub>2</sub> composites were prepared by direct calcination. The

School of Materials Science and Engineering, China University of Petroleum (East China), QingDao 266580, China. E-mail: enyangliu@126.com



heterojunction structure of g-C<sub>3</sub>N<sub>4</sub> with ZrO<sub>2</sub> greatly improved the efficiency of photocatalytic degradation of rhodamine B, and the reasons for its photocatalytic activity and photocatalytic mechanism were explored.

## 2. Experimental section

### 2.1 Catalysts preparation

All raw materials were of analytical grade and were not further purified. They were purchased from Sinopharm Chemical Reagent Network. Pure ZrO<sub>2</sub> was prepared from ZrOCl<sub>2</sub>·8H<sub>2</sub>O and stronger ammonia water. The method is as follows: 6.4450 g ZrOCl<sub>2</sub>·8H<sub>2</sub>O was added to 100 mL deionized water to prepare 0.2 mol L<sup>-1</sup> ZrOCl<sub>2</sub> aqueous solution. Slowly added stronger ammonia water to adjust pH to 10–11 and stirred for 1 h. Then, it was dried at 60 °C for 10 h and thoroughly ground to obtain a ZrO<sub>2</sub> precursor powder. The precursor powder was calcined at 500 °C for 3 h in a tube furnace at a heating rate of 5 °C min<sup>-1</sup> to obtain a ZrO<sub>2</sub> powder photocatalytic material. Pure g-C<sub>3</sub>N<sub>4</sub> was prepared as follows: 40 g of urea was added to 40 mL of deionized water, dissolved by ultrasonic for 1 h, and recrystallized by drying at 100 °C for 12 h. The crystal product was thoroughly ground, and the product was calcined at 550 °C for 4 h in a tube furnace at a heating rate of 2.3 °C min<sup>-1</sup>, to give a pale yellow g-C<sub>3</sub>N<sub>4</sub>.

The g-C<sub>3</sub>N<sub>4</sub>/ZrO<sub>2</sub> composites were prepared as follows: in the process of preparing the ZrO<sub>2</sub> precursor powder, after adjusted the pH to 10–11 and stirred uniformly, a certain amount of g-C<sub>3</sub>N<sub>4</sub> prepared in advance was added, and the mixture was stirred for 1 h to make the mixture uniform, dried at 60 °C, ground for 30 min, and then heated at 500 °C for 3 h in tube furnace with a heating rate of 5 °C min<sup>-1</sup>, to obtain g-C<sub>3</sub>N<sub>4</sub>/ZrO<sub>2</sub> composites. Among them, the g-C<sub>3</sub>N<sub>4</sub>/ZrO<sub>2</sub> composites were 5 : 1, 4 : 1, 3 : 1 and 2 : 1 by mass ratio (respectively recorded as 5 : 1 CN/ZrO<sub>2</sub>, 4 : 1 CN/ZrO<sub>2</sub>, 3 : 1 CN/ZrO<sub>2</sub> and 2 : 1 CN/ZrO<sub>2</sub>).

### 2.2 Catalyst characterizations

The crystal phase structure of the sample was measured using a X' Pert PRD MPD type Cu target X-ray diffractometer from the Dutch PANalytical B.V. at a scanning speed of 0.303841° s<sup>-1</sup>. The SEM was performed using a Japanese JSM-7200 field emission scanning electron microscope. The TEM used a Japanese JEM-2100 high-resolution transmission electron microscope. The PL spectrum was measured with a F-7000 type fluorescence spectrophotometer, using a Xe lamp (excitation wavelength is 365 nm) as light source. The DRS spectrum used a U-3900 UV-vis spectrophotometer and BaSO<sub>4</sub> as a reference sample. The FT-IR spectrums were collected with a Tensor II Fourier transform infrared spectrometer.

Electrochemical impedance spectroscopy (EIS) and photocurrent response (PR) tests were performed using the CS130 electrochemical workstation. A three-electrode system was used, and the corresponding three electrodes are a working electrode, a reference electrode (Ag/AgCl saturated KCl), and a counter electrode (Pt rod). The working electrode was prepared as follows: a 2 × 1 cm piece of indium tin oxide (ITO)

glass was cut, then washed with acetone, boiling NaOH (0.1 mol L<sup>-1</sup>) and deionized water. Then weighed 0.018 g of sample and 0.002 g of polyvinylidene fluoride mixed and fully ground. After the grinding, 60 μL of 1-methyl-2-pyrrolidone was added and ultrasonicated for 0.5 h, and then the resulting suspension was applied onto an ITO glass substrate to a coating area of 1 cm<sup>2</sup>. Finally, the coated ITO glass was dried at 50 °C to obtain a working electrode.<sup>31</sup> An alternating current voltage of 10 mV was applied, and the initial potential was 0 V. The EIS spectrum was made in 0.01 M Na<sub>2</sub>SO<sub>4</sub> in the frequency range of 10<sup>5</sup> Hz to 10<sup>-2</sup> Hz. The photocurrent response diagram was measured using a 350 W Xe lamp as the light source and an aqueous solution of Na<sub>2</sub>SO<sub>4</sub> (0.01 M) as the electrolyte.

### 2.3 Photocatalytic reaction

Using photocatalytic degradation of rhodamine (18 mg L<sup>-1</sup>) as a model reaction, the light source is a 250 W high-pressure mercury lamp, and the wavelength below 420 nm is filtered by a filtering device. Its light intensity is 7.0 mW cm<sup>-2</sup>, the photocatalytic properties of different ratios of CN/ZrO<sub>2</sub> composites and pure g-C<sub>3</sub>N<sub>4</sub> and ZrO<sub>2</sub> were investigated. Added a certain amount of photocatalytic materials (according to the amount of 0.08 g/100 mL) in the configured rhodamine solution. The sample was first darkly adsorbed for 20 minutes, then the solution was transferred to a light source for photodegradation reaction, and samples were taken at the same time. All samples were centrifuged twice after taking the supernatant. The absorbance was measured with a 752 UV-vis spectrophotometer. The maximum absorption wavelength of rhodamine was 554 nm. All samples were repeated for the above steps. The above tests were performed three times and averaged. The sample was recovered dry and subjected to a cycle test to test its cycle performance.

### 2.4 Mechanism exploration

In order to confirm the mechanism of this catalytic reaction, benzophenone (BQ), triethanolamine (TEOA) and *tert*-butanol (IPA) were used as scavengers for superoxide radicals (·O<sub>2</sub><sup>-</sup>),

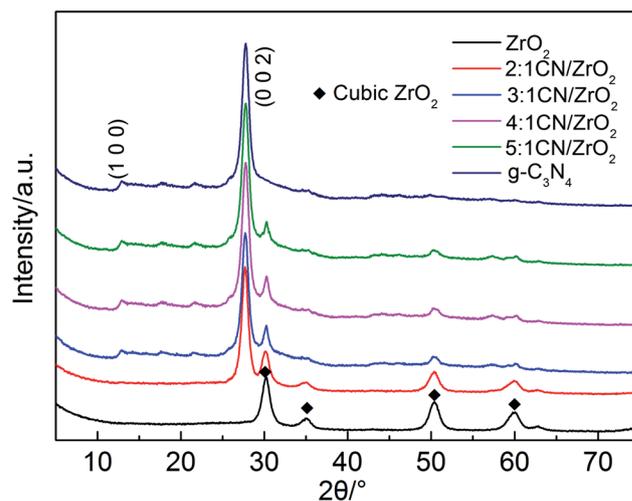


Fig. 1 XRD patterns of CN/ZrO<sub>2</sub> composites and pure g-C<sub>3</sub>N<sub>4</sub> and ZrO<sub>2</sub>.



holes ( $h^+$ ) and hydroxyl radicals ( $\cdot OH$ ). These three kinds of scavengers ( $0.01 \text{ mol L}^{-1}$ ) were added to three same rhodamine B solutions respectively before dark adsorption, and the rest of the process was consistent with the degradation experiment.<sup>32</sup>

### 3. Results and discussion

#### 3.1 XRD analysis

In order to determine the crystal phase structure of the semiconductor photocatalytic material, all samples were examined

using XRD. As shown in Fig. 1, the XRD patterns of  $g\text{-C}_3\text{N}_4$  corresponds to the strongest peak at  $2\theta = 27.4^\circ$ , and its crystal plane is (002), indicating periodic graphite deposition of conjugated aromatic CN units; at  $2\theta = 12.7^\circ$ , the diffraction peak corresponds to the (100) crystal plane, and is formed by hybridization of the aromatic substance  $sp^2$  in the layer, which has a 3 s-triazine structure.<sup>33</sup> The pure phase  $\text{ZrO}_2$  is a cubic phase, and the corresponding characteristic peaks are  $2\theta = 30.22^\circ$ ,  $35.27^\circ$ ,  $50.73^\circ$  and  $60.20^\circ$ , respectively. The  $\text{CN}/\text{ZrO}_2$  composites have only two peaks and no other phases, indicating

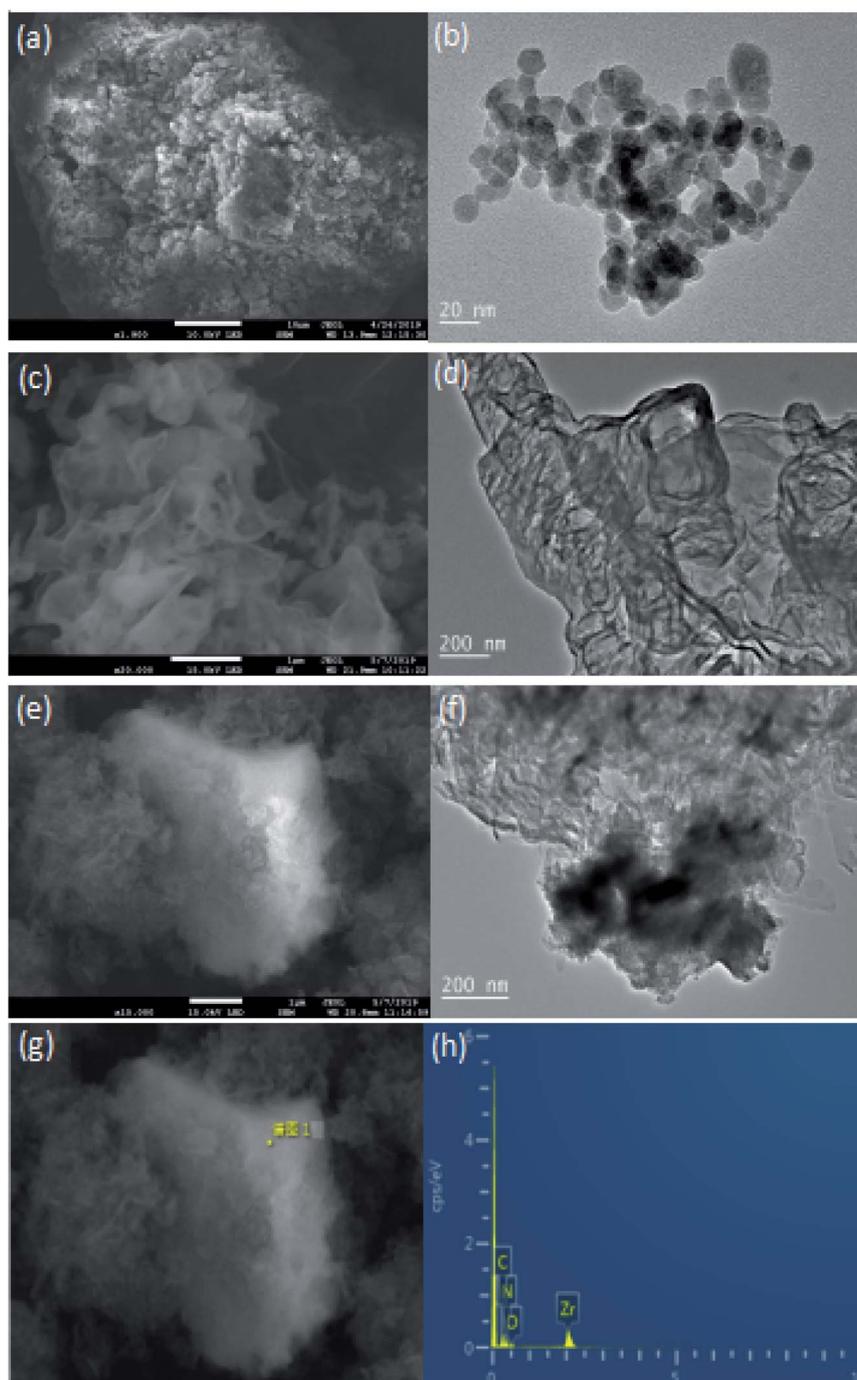


Fig. 2 SEM and TEM spectra of  $\text{ZrO}_2$  (a and b),  $g\text{-C}_3\text{N}_4$  (c and d),  $\text{CN}/\text{ZrO}_2$  composite (e and f) and EDS (g and h).



that the two  $g\text{-C}_3\text{N}_4$  and  $\text{ZrO}_2$  are well complexed, and as the amount of  $g\text{-C}_3\text{N}_4$  increases, the peak intensity increases and the peak intensity of  $\text{ZrO}_2$  decreases.

### 3.2 Characterization of morphology and structure

SEM and TEM spectras of  $\text{CN}/\text{ZrO}_2$  composites and pure  $g\text{-C}_3\text{N}_4$  and  $\text{ZrO}_2$  were observed in order to observe the morphology and structure of the samples. It can be seen from the Fig. 2(a) and (b) that the pure  $\text{ZrO}_2$  is an irregular particle and has a certain agglomeration, and its average particle diameter is 15.4 nm. It can be seen from Fig. 2(c) and (d) that the pure  $g\text{-C}_3\text{N}_4$  is a lamellar structure and exhibits multi-piece aggregation phenomenon. Because the morphology of the two materials is completely different, it is easy to distinguish in scanning electron microscopy. It can be clearly seen in Fig. 2(e) that the white irregular mass is  $\text{ZrO}_2$  and is coated with flaky  $g\text{-C}_3\text{N}_4$ , indicating that the two are well compounded, and the TEM spectrum (Fig. 2(f)) can also be. It is seen that the darker color is  $\text{ZrO}_2$ , because it is covered by  $g\text{-C}_3\text{N}_4$ , so the graininess is not obvious. To further confirm, the Fig. 2(e) EDS component analysis is shown in Fig. 1(g) and (h). It is observed that the C, N, O and Zr elements are all included. It shows that  $\text{ZrO}_2$  is coated with  $g\text{-C}_3\text{N}_4$  and is well compounded.

### 3.3 Functional group studies

The FT-IR spectrum of  $\text{CN}/\text{ZrO}_2$  composite materials and pure  $g\text{-C}_3\text{N}_4$  and  $\text{ZrO}_2$  is shown in Fig. 3. The pure  $g\text{-C}_3\text{N}_4$  has a sharp absorption peak at  $808\text{ cm}^{-1}$ , and a strong absorption peak in the range of  $1200\text{--}1700\text{ cm}^{-1}$ . This is caused by the bending vibration of the 3 *s*-triazine C–N bond.<sup>34</sup> From  $3040\text{ cm}^{-1}$  to  $3302\text{ cm}^{-1}$  corresponds to a broad absorption peak of  $g\text{-C}_3\text{N}_4$ , which is caused by the group of the aromatic ring defect. Pure  $\text{ZrO}_2$  has absorption peaks around  $509\text{ cm}^{-1}$  and  $750\text{ cm}^{-1}$  due to the stretching vibration of Zr–O. The broad absorption peak is around  $3373\text{ cm}^{-1}$ , caused by hydroxyl groups on the surface of the hydrated oxide and adsorbed water.<sup>35</sup> The FT-IR of  $\text{CN}/\text{ZrO}_2$  composites is similar to that of pure phase  $g\text{-C}_3\text{N}_4$ . With the

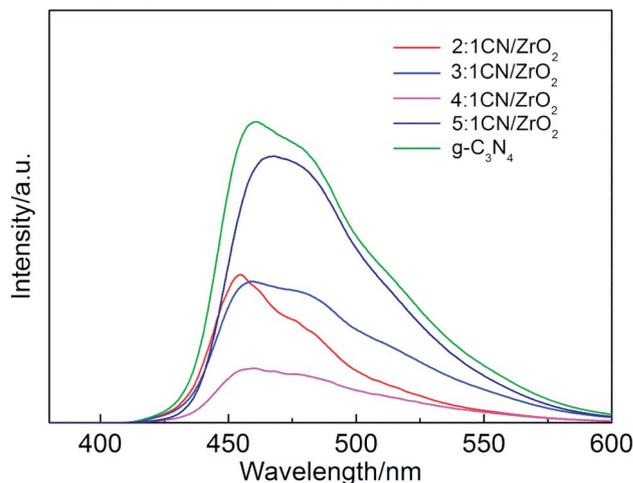


Fig. 4 PL spectrum of  $\text{CN}/\text{ZrO}_2$  composites and pure  $g\text{-C}_3\text{N}_4$ .

addition of  $\text{ZrO}_2$ , it varies around  $509\text{ cm}^{-1}$  and  $3373\text{ cm}^{-1}$ . It can be seen that the FT-IR spectrum is consistent with the XRD results, indicating the formation of a  $\text{CN}/\text{ZrO}_2$  heterostructure.

### 3.4 Photoluminescence spectroscopy

The photoluminescence spectroscopies of  $\text{CN}/\text{ZrO}_2$  composites and pure  $g\text{-C}_3\text{N}_4$  are shown in Fig. 4. The effect of  $\text{CN}/\text{ZrO}_2$  composites heterojunction on the separation efficiency of electron–hole pairs was investigated. It can be seen from Fig. 4 that the pure  $g\text{-C}_3\text{N}_4$  has a strong emission peak around 460 nm, which can be attributed to the band gap transition emission, and the energy of the emitted light approximates the band gap energy. The fluorescence emission intensity of  $\text{CN}/\text{ZrO}_2$  composites is greatly inhibited compared with that of pure  $g\text{-C}_3\text{N}_4$ . With the increase of  $\text{CN}/\text{ZrO}_2$  ratio, the degree of fluorescence quenching decreases first and then increases. It is indicated that the electron–hole recombination rate decreases first and then increases, and the 4 : 1  $\text{CN}/\text{ZrO}_2$  composite recombination rate is the lowest.

### 3.5 Electrochemical test

In order to confirm the results obtained by the PL spectrum, electrochemical impedance (EIS) and transient photocurrent response experiments were further performed. The EIS spectrum is shown in Fig. 5(a). The diameter of the semi-arc is equivalent to the charge transfer resistance of the catalyst. The smaller the radius, the smaller the resistance, the higher the electron–hole pair separation efficiency of the sample, and the faster the interface charge transfer will be. It can be seen from the Fig. 5(a) that the radius of the 4 : 1  $\text{CN}/\text{ZrO}_2$  composite is the smallest, that is, the charge transfer resistance is the smallest, indicating that the addition of  $\text{ZrO}_2$  is beneficial to the separation of photogenerated electron–hole pairs and enhance the photocatalytic activity of the sample. The transient photocurrent response of the semiconductor photocatalyst is also directly related to the recombination rate of the electron–hole pair.<sup>36</sup> Fig. 5(b) shows the transient photocurrent response of

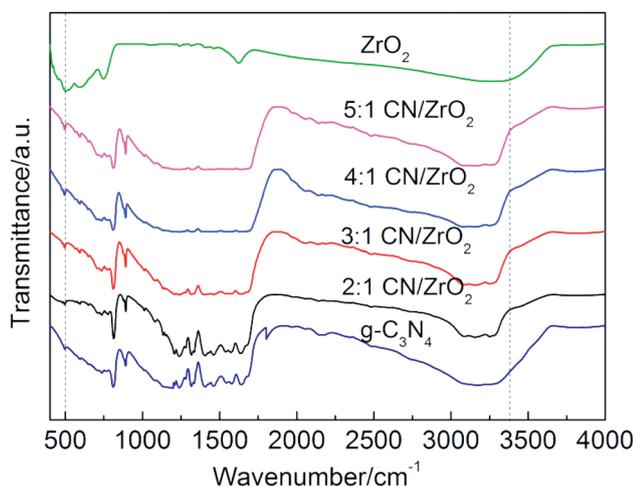


Fig. 3 FT-IR spectra of  $\text{CN}/\text{ZrO}_2$  composites and pure  $g\text{-C}_3\text{N}_4$ ,  $\text{ZrO}_2$ .



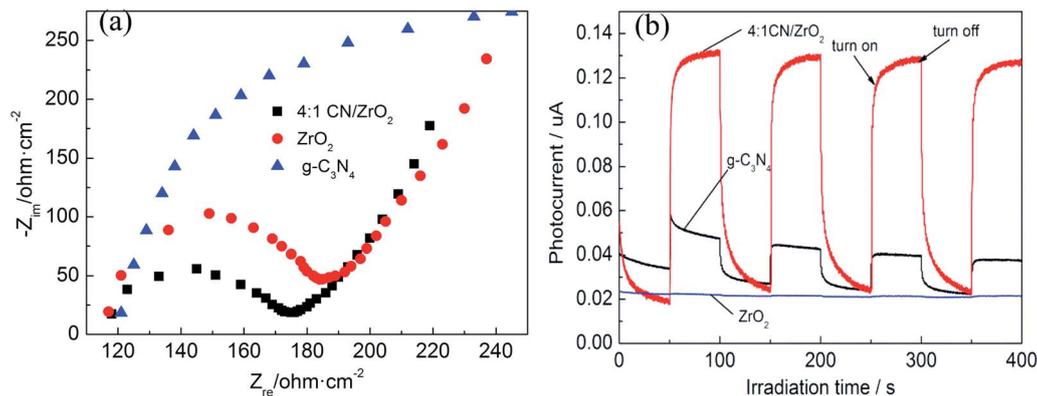


Fig. 5 EIS changes (a) and transient photocurrent responses (b) of 4 : 1 CN/ZrO<sub>2</sub> and pure g-C<sub>3</sub>N<sub>4</sub>, ZrO<sub>2</sub> electrodes.

4 : 1 CN/ZrO<sub>2</sub> and pure phase g-C<sub>3</sub>N<sub>4</sub> and ZrO<sub>2</sub>. As can be seen, both the 4 : 1 CN/ZrO<sub>2</sub> composite and the pure g-C<sub>3</sub>N<sub>4</sub> can be excited under visible light and produce a stable photocurrent response, indicating the presence of photogenerated carriers in the sample. However, pure ZrO<sub>2</sub> can hardly be excited under visible light, and only a very small amount of photogenerated carriers exists. Under the illumination of the light source, the photocurrent density of 4 : 1 CN/ZrO<sub>2</sub> is greatly improved, which is about 3 times that of g-C<sub>3</sub>N<sub>4</sub>. It is shown that the addition of ZrO<sub>2</sub> effectively inhibits the recombination of g-C<sub>3</sub>N<sub>4</sub> electron-hole pairs, which also enhances its photocatalytic activity.

### 3.6 Optical performance studies

The UV-vis DRS of CN/ZrO<sub>2</sub> and pure phase g-C<sub>3</sub>N<sub>4</sub> and ZrO<sub>2</sub> is shown in Fig. 6. In order to detect the optical properties of the sample, UV-vis DRS was performed on CN/ZrO<sub>2</sub> and pure g-C<sub>3</sub>N<sub>4</sub>, ZrO<sub>2</sub>. The cut line method is used to make the tangent and the intersection with the abscissa to obtain the absorption wavelength threshold. It can be seen from Fig. 6 that the maximum absorption wavelength of ZrO<sub>2</sub> for light is 247 nm. The pure g-C<sub>3</sub>N<sub>4</sub> can absorb light at a maximum wavelength of 428 nm, compared with the pure g-C<sub>3</sub>N<sub>4</sub>, the absorption band edge of CN/ZrO<sub>2</sub> is red-shifted, and the absorption of visible light is significantly enhanced. The 4 : 1 CN/ZrO<sub>2</sub> composite

absorption band can reach 465 nm, which indicates that the incorporation of ZrO<sub>2</sub> improves the visible light absorption performance of g-C<sub>3</sub>N<sub>4</sub>, and 4 : 1 CN/ZrO<sub>2</sub> is the best compound ratio.

Calculate the forbidden band width of a semiconductor according to the Kubelka-Munk formula:<sup>37,38</sup>

$$(\alpha hv)^{1/n} = A(hv - E_g) \quad (1)$$

where  $\alpha$  is the absorption coefficient,  $h$  is the Planck constant, and  $\nu$  is the frequency of light.  $A$  is a constant and  $E_g$  is the forbidden band energy. The  $n$  value of ZrO<sub>2</sub> and g-C<sub>3</sub>N<sub>4</sub> is 1/2.<sup>39,40</sup> As shown in Fig. 6(b), the bandgaps of the samples were estimated to be 2.68 eV, 2.82 eV and 4.91 eV corresponding to 4 : 1 CN/ZrO<sub>2</sub>, g-C<sub>3</sub>N<sub>4</sub> and ZrO<sub>2</sub>, respectively, which were close to the known values in previous reports.<sup>31</sup> It also explained the 4 : 1 CN/ZrO<sub>2</sub> composite has better light absorption properties than g-C<sub>3</sub>N<sub>4</sub>, which may be due to the interaction of ZrO<sub>2</sub> with g-C<sub>3</sub>N<sub>4</sub>. Some chemical bonds formed between the two semiconductors may result in an increase in optical properties.

### 3.7 Catalytic performance evaluation

The photocatalytic activity of CN/ZrO<sub>2</sub> and pure g-C<sub>3</sub>N<sub>4</sub> and ZrO<sub>2</sub> was evaluated by degrading RhB under visible-light. Fig. 7a-d show the absorption spectra of RhB with different

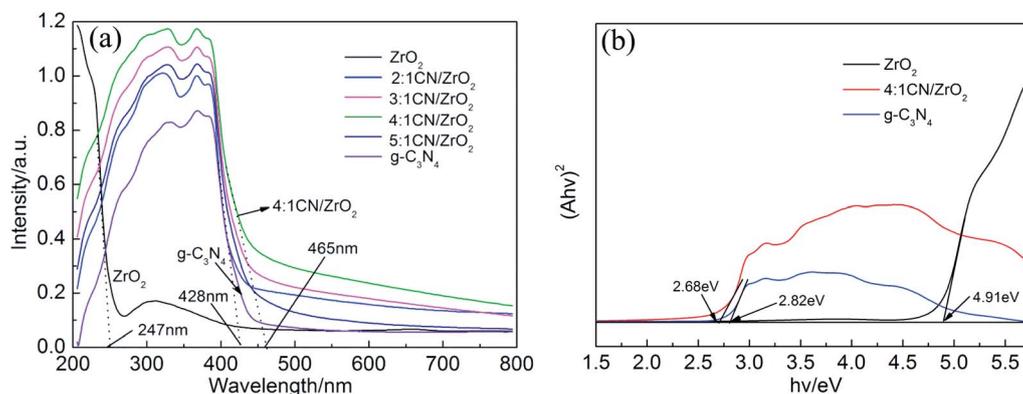


Fig. 6 UV-vis spectra of CN/ZrO<sub>2</sub> composites and pure g-C<sub>3</sub>N<sub>4</sub>, ZrO<sub>2</sub> (a); the transformed diffuse reflectance spectra (b).



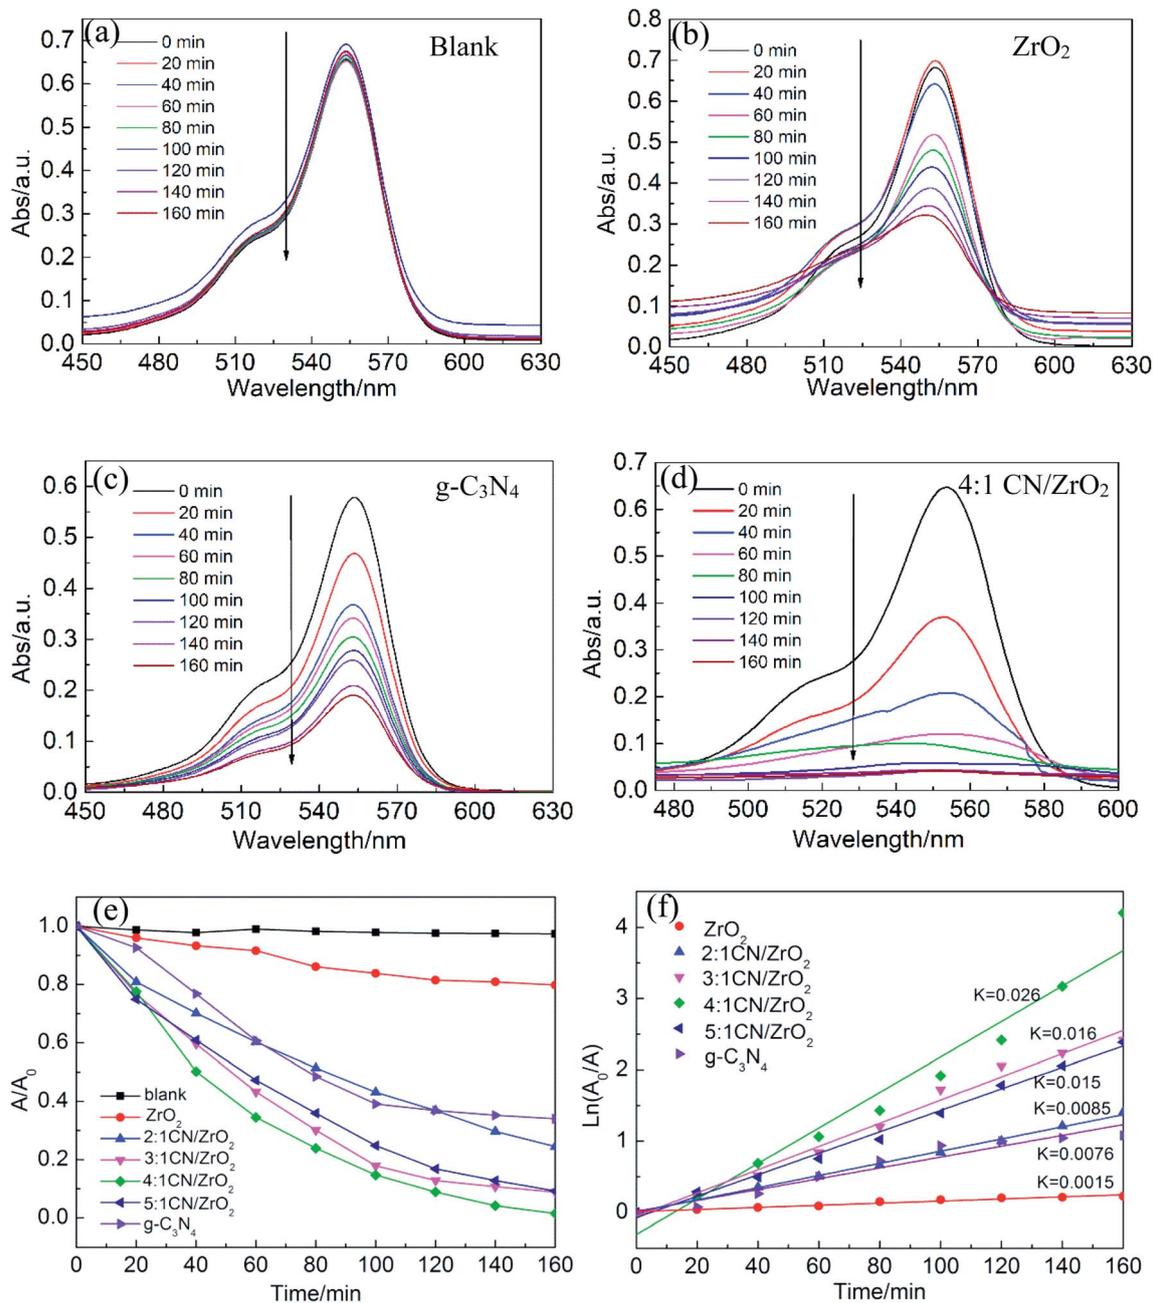


Fig. 7 UV-vis absorption spectra of photocatalytic RhB degradation over (a) blank, (b) ZrO<sub>2</sub>, (c) g-C<sub>3</sub>N<sub>4</sub> and (d) CN/ZrO<sub>2</sub> under the light irradiation. (e) Photodegradation efficiency toward RhB measured at 554 nm and (f) the photocatalytic rate curves and corresponding fitted kinetics curves of the blank experiment, ZrO<sub>2</sub>, g-C<sub>3</sub>N<sub>4</sub>, and CN/ZrO<sub>2</sub> composites under the light irradiation.

concentrations during the photocatalytic reaction. For the blank experiment, the absorption intensity at 554 nm remains almost unchanged with the increasing irradiation time as shown in Fig. 7(a), indicating the photolysis of RhB molecules is almost negligible. Adding a photocatalyst prepared in advance to the catalytic system, the RhB concentration gradually decreases with the extension of the catalytic time, as shown in Fig. 7(b)–(d). With the same catalytic time, the catalytic efficiency CN/ZrO<sub>2</sub> > g-C<sub>3</sub>N<sub>4</sub> > ZrO<sub>2</sub>. After catalysis, the maximum absorption wavelength of RhB is still around 554 nm, indicating that the sample has little effect on RhB. Test the specific

photocatalytic efficiency as shown in Fig. 7(e) and (f). It can be seen from the Fig. 7(e) that the direct degradation of RhB can be neglected (<5%). The degradation of pure ZrO<sub>2</sub> is very poor, with only a small amount of adsorption and degradation, and the final degradation rate can only reach 20.2%. The degradation of pure g-C<sub>3</sub>N<sub>4</sub> is better than that of ZrO<sub>2</sub>, but the final degradation rate can only reach 66%, and the effect is not satisfactory. After the addition of ZrO<sub>2</sub>, the adsorption and degradation ability of g-C<sub>3</sub>N<sub>4</sub> has been significantly improved. With the increase of ZrO<sub>2</sub> addition, the catalytic effect under visible light first becomes better and then deteriorates. 4 : 1 CN/ZrO<sub>2</sub> is the best



Table 1 Some g-C<sub>3</sub>N<sub>4</sub> composite materials and degradation rate table

Sample	SnO <sub>2</sub> -ZnO/g-C <sub>3</sub> N <sub>4</sub> (ref. 41)	CeO <sub>2</sub> /P-C <sub>3</sub> N <sub>4</sub> (ref. 42)	Ag/g-C <sub>3</sub> N <sub>4</sub> (ref. 43)	BiV/g-C <sub>3</sub> N <sub>4</sub> (ref. 44)
Degradation rate	0.0184 min <sup>-1</sup>	0.0110 min <sup>-1</sup>	0.01576 min <sup>-1</sup>	0.101 min <sup>-1</sup>

compound ratio, and the final catalytic degradation rate can reach 98.5%. The catalyst with high catalytic efficiency also has good adsorption performance, but its catalytic activity is not completely dependent on the adsorption capacity. The adsorption performance of 4 : 1 CN/ZrO<sub>2</sub> is not optimal, but the photocatalytic degradation is the best. From Fig. 7(f) photocatalytic degradation rate map, the degradation rate of pure g-C<sub>3</sub>N<sub>4</sub> is 0.0076 min<sup>-1</sup>, which is five times the degradation rate of ZrO<sub>2</sub> (0.0015 min<sup>-1</sup>). After g-C<sub>3</sub>N<sub>4</sub> is combined with ZrO<sub>2</sub>, the electron-hole separation efficiency and visible light absorption capacity can be significantly improved. With the increase of ZrO<sub>2</sub> compounding amount, the degradation rate of g-C<sub>3</sub>N<sub>4</sub>/ZrO<sub>2</sub> composites increases first and then decreases. 4 : 1 CN/ZrO<sub>2</sub> composite have the highest degradation rate, up to 0.026 min<sup>-1</sup>, which is 3.4 times that of pure g-C<sub>3</sub>N<sub>4</sub>.

The predecessors have also done a lot of modification of g-C<sub>3</sub>N<sub>4</sub>. Some composite materials and degradation rates are shown in Table 1. Prabhakar vattikuti *et al.*<sup>41</sup> have prepared SnO<sub>2</sub>-ZnO/g-C<sub>3</sub>N<sub>4</sub> composites. The degradation rate is 0.0184 min<sup>-1</sup>, which is 5 times that of pure g-C<sub>3</sub>N<sub>4</sub>. The degradation rate of CeO<sub>2</sub>/P-C<sub>3</sub>N<sub>4</sub> prepared by J. Luo *et al.*<sup>42</sup> can reach 0.011 min<sup>-1</sup>, which is 4 times higher than that of pure g-C<sub>3</sub>N<sub>4</sub>. Nagajyothi *et al.*<sup>43</sup> doped g-C<sub>3</sub>N<sub>4</sub> with Ag greatly increase the degradation rate, which can reach 0.01576 min<sup>-1</sup>, which is 2.5 times higher than that of pure g-C<sub>3</sub>N<sub>4</sub>. Prabhakar vattikuti *et al.*<sup>44</sup> also prepared BiV/g-C<sub>3</sub>N<sub>4</sub>, the degradation rate can reach 0.101 min<sup>-1</sup>, which is 2.5 times higher than BiV. Compared with the composites prepared by the predecessors, the degradation rate of the CN/ZrO<sub>2</sub> composites prepared in this paper increased greatly.

### 3.8 Cycle performance and catalytic mechanism

For photocatalytic materials, not only photocatalytic performance is required, but also good stability is required, which can be reused without losing activity. Therefore, 4 : 1 CN/ZrO<sub>2</sub>

composite cycle test was carried out, and the sample was recovered, dried, and ground at the end of each test, and then subjected to the next round of tests, which were cycled five times in total. The cycle performance is shown in Fig. 8(a). After five cycles of the sample circulation, the degradation effect is not significantly reduced, indicating that the sample has good stability and can be reused for degrading wastewater. The photocatalytic mechanism was studied. As shown in Fig. 8(b), the photocatalytic effect of *tert*-butanol (TBA) and triethanolamine (TEOA) was not significantly decreased in the pure g-C<sub>3</sub>N<sub>4</sub> system. After the addition of benzoquinone (BQ), the degradation rate decreased from 66% to 21.3%, indicating that ·O<sub>2</sub><sup>-</sup> is the main active species. In the g-C<sub>3</sub>N<sub>4</sub>/ZrO<sub>2</sub> system, the photocatalytic effect was not significantly reduced after the addition of *tert*-butanol (TBA). After the addition of benzoquinone (BQ), the degradation rate decreased from 98.5% to 32.1%, and the degradation rate after adding triethanolamine reduced to 49%, indicating that ·O<sub>2</sub><sup>-</sup> and h<sup>+</sup> work together in the reaction process in the g-C<sub>3</sub>N<sub>4</sub>/ZrO<sub>2</sub> system.

Further study on the changes of active species in the reaction process, in which the semiconductor VB and CB have the following formula:<sup>42</sup>

$$E_{CB} = X - E^{\circ} - \frac{E_g}{2} \quad (2)$$

$$E_{VB} = E_{CB} + E_g \quad (3)$$

$E^{\circ}$  is a constant relative to the standard H electrode, its value is 4.5 eV,  $E_g$  is the band gap,  $X$  is the absolute electronegativity, and  $X$  values of g-C<sub>3</sub>N<sub>4</sub> and ZrO<sub>2</sub> are 4.73 eV and 5.91 eV, respectively.<sup>31,45,46</sup>  $E_{VB}$  values of g-C<sub>3</sub>N<sub>4</sub> and ZrO<sub>2</sub> were calculated to be 1.64 eV and 3.86 eV, respectively, and  $E_{CB}$  values were -1.18 eV and -1.05 eV.  $E_{VB}$  values of g-C<sub>3</sub>N<sub>4</sub> and ZrO<sub>2</sub> are lower than the potentials of ·OH/H<sub>2</sub>O (+1.99 eV) and ·OH/OH<sup>-</sup> (+2.68 eV), so H<sub>2</sub>O and OH<sup>-</sup> cannot be oxidized to ·OH by valence

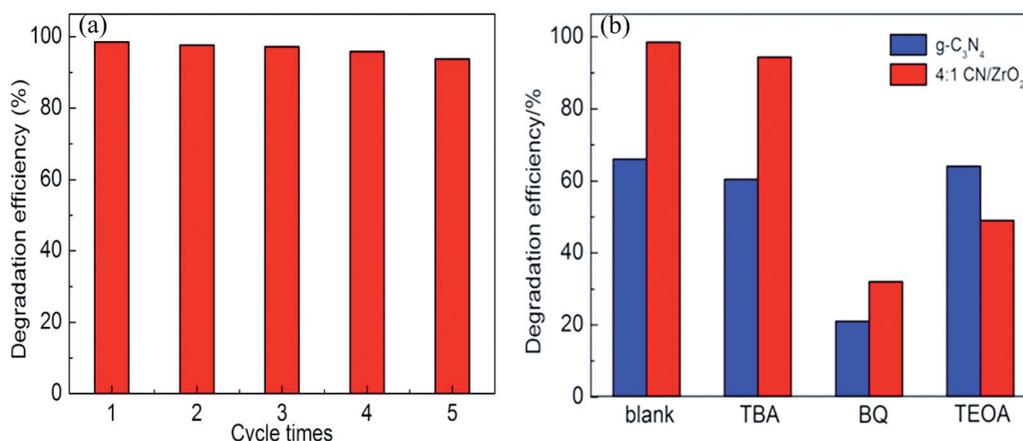


Fig. 8 Photocatalytic cycle performance of 4 : 1 CN/ZrO<sub>2</sub> (a) and reactant capture diagram (b).






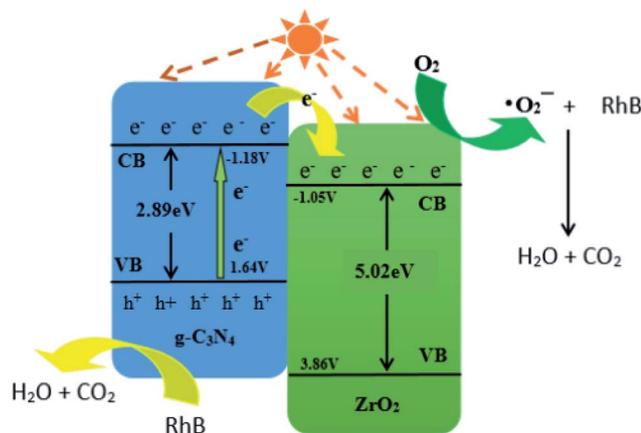


Fig. 9 Catalytic mechanism diagram of CN/ZrO<sub>2</sub> composites.

band holes. Therefore,  $\cdot\text{OH}$  is not an active species in the system. The potential of  $\text{O}_2/\cdot\text{O}_2^-$  is  $-0.33$  eV, which is higher than  $E_{\text{CB}}$  values of  $g\text{-C}_3\text{N}_4$  and  $\text{ZrO}_2$ , so  $\text{O}_2$  can be reduced to  $\cdot\text{O}_2^-$ , and the RhB is degraded by strong reduction of  $\cdot\text{O}_2^-$ . In the CN/ZrO<sub>2</sub> system, electrons in  $g\text{-C}_3\text{N}_4$  are excited from VB to CB under visible light irradiation, thereby generating holes in the VB of the semiconductor. Due to the difference in CB potential, the photogenerated electrons on the surface of  $g\text{-C}_3\text{N}_4$  easily migrate to the CB of  $\text{ZrO}_2$ , while the holes remain on the VB of  $g\text{-C}_3\text{N}_4$ . The forbidden band energy of  $\text{ZrO}_2$  is too large, and the energy of visible light is not enough to excite electrons on the valence band to the conduction band. The electrons transferred from  $g\text{-C}_3\text{N}_4$  on the  $\text{ZrO}_2$  conduction band will not jump to the valence band. This can be considered as a single transfer mechanism.<sup>47</sup> The system can effectively improve the separation of photogenerated electron-hole pairs, greatly reducing the possibility of charge recombination, resulting in high photocatalytic activity of CN/ZrO<sub>2</sub> composites. It can be seen from the above PL, photocurrent and catalytic performance that the recombination of electron-hole pairs is suppressed, and the direct oxidation ability of holes is greatly improved, so that  $\text{h}^+$  and  $\cdot\text{O}_2^-$  are collectively active species in the CN/ZrO<sub>2</sub> system. From the mechanism diagram (Fig. 9), the interface between  $g\text{-C}_3\text{N}_4$  and  $\text{ZrO}_2$  greatly affects the separation efficiency of electron-hole pairs. If a large amount of  $\text{ZrO}_2$  is present, the contact area is reduced, thereby reducing the separation efficiency and further reducing the photocatalytic performance. Therefore, the optimal ratio of CN/ZrO<sub>2</sub> composite material exists. The specific process of catalytic degradation of RhB by CN/ZrO<sub>2</sub> composites is as follows:



## 4. Conclusion

The high catalytic activity of CN/ZrO<sub>2</sub> composite photocatalyst was obtained by directly calcining the mixture of  $g\text{-C}_3\text{N}_4$  and  $\text{ZrO}_2$  precursor. Among them, 4 : 1 CN//ZrO<sub>2</sub> exhibited the highest degradation of RhB under visible light. The final catalytic efficiency can reach 98.5%. This is because the combination of  $g\text{-C}_3\text{N}_4$  and  $\text{ZrO}_2$  reduces the charge transfer resistance and effectively suppresses the recombination of electron-hole pairs, thereby improving the photocatalytic activity. At the same time, the cycle test shows that the prepared catalyst has good stability and can be reused many times, so this catalyst has broad application prospects in solving environmental pollution.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was supported by the Natural Science Foundation of Shandong Province of China (No. ZR2019MEM020, No. ZR2017LEM004), the Fundamental Research Funds for the Central Universities of China (No. 18CX02091A) and the Open Fund (No. OGE201702-07) of Key Laboratory of Oil & Gas Equipment, Ministry of Education (Southwest Petroleum University).

## References

- 1 F. E. Osterloh, *Chem. Soc. Rev.*, 2013, **42**, 2294–2320, DOI: 10.1039/c2cs35266d.
- 2 Y. Qu and X. Duan, *Chem. Soc. Rev.*, 2013, **42**, 2568–2580, DOI: 10.1002/chin.201324 226.
- 3 Y. Hou, Z. Wen, S. Cui, S. Ci, S. Mao and J. Chen, *Adv. Funct. Mater.*, 2015, **25**, 872–882, DOI: 10.1002/adfm.201403657.
- 4 M. Li, W. Luo, D. Cao, X. Zhao, Z. Li and T. Yu, *Angew. Chem. Int. Ed.*, 2013, **52**, 11016–11020, DOI: 10.1002/anie.201305350.
- 5 Y. Li, T. Takata, D. Cha, K. Takanebe, T. Minegishi and J. Kubota, *Adv. Mater.*, 2013, **25**, 125–131, DOI: 10.1002/adma.201202582.
- 6 Y. Li, H. Zhang, P. Liu, D. Wang, Y. Li and H. Zhao, *Small*, 2013, **9**, 3336–3344, DOI: 10.7150/jca.16961.
- 7 Y. S. Jun, E. Z. Lee, X. Wang, W. H. Hong, G. D. Stucky and A. Thomas, *Adv. Funct. Mater.*, 2013, **23**, 3661–3667.
- 8 K. Sridharan, E. Jang and T. J. Park, *Appl. Catal. B Environ.*, 2013, **142**, 718–728, DOI: 10.1007/s11664-015-4280-9.
- 9 L. Hairui, L. Man, Y. Jien, H. Chunjie, S. Jun and Z. Haifa, *Mater. Res. Bull.*, 2018, 10619–10627, DOI: 10.1016/j.materresbull.2018.05.026.
- 10 M. Zeng, Y. Z. Li, M. Y. Mao, J. L. Bai and L. R. X. J. Zhao, *ACS Catal.*, 2015, **5**, 3278–3286, DOI: 10.1021/acscatal.5b00292.
- 11 J. M. Wu and T. K. Wei, *J. Phys. Chem. C*, 2015, **119**, 1433–1441, DOI: 10.1021/acs.jpcc.5b02057.
- 12 J. Su, L. Guo, N. Bao and C. A. Grimes, *Nano Lett.*, 2011, **11**, 1928–1933, DOI: 10.1021/nl2000743.



- 13 T. Ohno, M. Akiyoshi, T. Umabayashi, K. Asai, T. Mitsui and M. Matsumura, *Appl. Catal., A*, 2004, **265**, 115–121, DOI: 10.1016/j.apcata.2004.01.007.
- 14 R. A. Senthil, J. Theerthagiri, A. Selvi and J. Madhavan, *Opt. Mater.*, 2017, **64**, 533–539, DOI: 10.1016/j.optmat.2017.01.025.
- 15 X. Wang, K. Maeda, A. Thomas, K. Takanabe, G. Xin and J. M. Carlsson, *Nat. Mater.*, 2009, **8**, 76–80, DOI: 10.1038/nmat2317.
- 16 Z. W. Zhao, Y. J. Sun and F. Dong, *Nanoscale*, 2014, **7**, 15–37, DOI: 10.1039/C4NR03008G.
- 17 J. Xu, H. T. Wu, X. Wang, B. Xue, Y. X. Li and Y. Cao, *Phys. Chem. Chem. Phys.*, 2013, **15**, 4510–4517, DOI: 10.1039/C3CP44402C.
- 18 G. Liao, S. Chen, X. Quan, H. T. Yu and H. M. Zhao, *J. Mater. Chem.*, 2012, **22**, 2721–2726, DOI: 10.1039/C1JM13490F.
- 19 J. Hong, X. Xia, Y. Wang and R. Xu, *J. Mater. Chem.*, 2012, **22**, 15006–15012, DOI: 10.1039/C2JM32053C.
- 20 X. Wang, K. Maeda, A. Thomas, K. Takanabe, G. Xin and J. M. Carlsson, *Nat. Mater.*, 2009, **8**, 76–80, DOI: 10.1038/nmat2317.
- 21 M. Fan, C. Song, T. Chen, Y. Xu, D. Xu and G. Wei, *RSC Adv.*, 2016, **6**, 34633–34640, DOI: 10.1039/c5ra27755h.
- 22 Y. S. C. Yan, Z. S. Li and Z. G. Zou, *Langmuir*, 2010, **26**, 3894–3901, DOI: 10.1021/la904023j.
- 23 X. C. Wang, K. Maeda, X. F. Chen, K. Takanabe, K. Domen, Y. D. Hou, X. Z. Fu and M. Antonietti, *J. Am. Chem. Soc.*, 2009, **131**, 1680–1691, DOI: 10.1021/ja809307s.
- 24 Y. Meng, J. Shen, D. Chen and G. Xin, *Rare Met.*, 2011, **30**, 276–279, DOI: 10.1007/s12598-011-0284-7.
- 25 T. Li, L. Zhao, Y. He, J. Cai, M. Luo and J. Lin, *Appl. Catal. B Environ.*, 2013, **129**, 255–263, DOI: 10.1016/j.apcatb.2012.09.031.
- 26 Y. M. He, J. Cai, L. H. Zhang, X. X. Wang, H. J. Lin, B. T. Teng, L. H. Zhao, W. Z. Weng, H. L. Wan and M. H. Fan, *Ind. Eng. Chem. Res.*, 2012, **53**, 5905–5915, DOI: 10.1021/ie4043856.
- 27 Y. Zang, L. Li, Z. Ying, H. Lin, G. Li and X. Guan, *RSC Adv.*, 2013, **3**, 13646–13650, DOI: 10.1039/C3RA41982G.
- 28 P. He, L. Song, S. Zhang, X. Wu and Q. Wei, *Mater. Res. Bull.*, 2014, **51**, 432–437, DOI: 10.1016/j.materresbull.2013.12.064.
- 29 X. Wang, J. Chen, X. Guan and L. Guo, *Int. J. Hydrogen Energy*, 2015, **40**, 7546–7552, DOI: 10.1016/j.ijhydene.2014.11.055.
- 30 J. Lv, K. Dai and J. Zhang, *Sep. Purif. Technol.*, 2017, **178**, 6–17.
- 31 X. Wang, L. Zhang, H. Lin, Q. Nong, W. Ying and T. Wu, *RSC Adv.*, 2014, **4**, 40029–40035, DOI: 10.1039/C4RA06035K.
- 32 Y. Hong, C. Li, G. Zhang, Y. Meng, B. Yin and Y. Zhao, *Chem. Eng. J.*, 2016, **299**, 74–84, DOI: 10.1016/j.cej.2016.04.092.
- 33 F. Dong, Z. Wang, Y. Sun, W. K. Ho and H. Zhang, *J. Colloid Interface Sci.*, 2013, **401**, 70–79, DOI: 10.1016/j.jcis.2013.03.034.
- 34 H. J. Yan and H. X. Yang, *J. Alloys Compd.*, 2011, **509**, 26–29, DOI: 10.1016/j.jallcom.2010.09.201.
- 35 X. Gao, Y. Q. Zhang, J. Sun and F. K. Shao, *Appl. Catal. Gen.*, 2013, **466**, 233–239.
- 36 H. Liu, S. A. Cheng, M. Wu, H. J. Wu, J. Q. Zhang and W. Z. Li, *J. Phys. Chem. A*, 2000, **104**, 7016–7020, DOI: 10.1021/jp000171q.
- 37 C. Y. Feng, Y. C. Deng, L. Tang, G. M. Zeng, J. J. Wang, J. F. Yu, Y. N. Liu, B. Peng, H. P. Feng and J. J. Wang, *Appl. Catal., B*, 2018, **239**, 525–536, DOI: 10.1016/j.apcatb.2018.08.049.
- 38 C. Y. Feng, L. Tang, Y. C. Deng, G. M. Zeng, J. J. Wang, Y. N. Liu, Z. M. Chen, J. F. Yu and J. J. Wang, *Appl. Catal., B*, 2019, **256**, 117827, DOI: 10.1016/j.apcatb.2018.08.049.
- 39 X. Wu, S. Yin, B. Liu, M. Kobayashi, M. Kakihana and T. Sato, *J. Mater. Chem. A*, 2014, **2**, 20832–20840, DOI: 10.1039/C4TA04132A.
- 40 J. Luo, G. Dong, Y. Zhu, Z. Yang and C. Wang, *Appl. Catal. B Environ.*, 2017, **214**, 46–56.
- 41 S. V. Prabhakar Vattikuti, P. A. Kumar Reddy, J. Shim and C. Byon, *ACS Omega*, 2018, **3**, 7587–7602, DOI: 10.1021/acsomega.8b00471.
- 42 J. Luo, X. Zhou, L. Ma and X. Xu, *RSC Adv.*, 2015, **5**, 68728–68735, DOI: 10.1039/C5RA10848A.
- 43 P. C. Nagajothi, M. Pandurangan, S. V. P. Vattikuti, C. O. Tettey, T. V. M. Sreekanth and J. Shim, *Sep. Purif. Technol.*, 2017, **188**, 228–237.
- 44 S. V. Prabhakar Vattikuti, P. A. Kumar Reddy, J. Shim and C. Byon, *Appl. Surf. Sci.*, 2018, **447**, 740–756, DOI: 10.1016/j.apsusc.2018.04.040.
- 45 S. Chen, Y. Hu, S. Meng and X. Fu, *Appl. Catal. B Environ.*, 2014, **150–151**, 564–573, DOI: 10.1016/j.apcatb.2013.12.053.
- 46 K. Huang, C. Liu, X. Yan, C. Y. Huang, J. B. Chen, M. Y. Chen, W. D. Shi and C. B. Liu, *Crystengcomm*, 2016, **18**, 6453–6463, DOI: 10.1016/j.seppur.2017.07.026.
- 47 L. Tang, C. Y. Feng, Y. C. Deng, G. M. Zeng, J. J. Wang, Y. N. Liu, H. P. Feng and J. J. Wang, *Appl. Catal., B*, 2018, **230**, 102–114, DOI: 10.1016/j.apcatb.2018.02.031.

