


 Cite this: *RSC Adv.*, 2020, 10, 13855

Promotion effect of urchin-like $\text{MnO}_x@PrO_x$ hollow core–shell structure catalysts for the low-temperature selective catalytic reduction of NO with NH_3

 Shuyuan Cheng,^a Jing Shao,^a Bichun Huang,^{*abc} Jinkun Guan^a and Lusha Zhou^a

A $\text{MnO}_x@PrO_x$ catalyst with a hollow urchin-like core–shell structure was prepared using a sacrificial templating method and was used for the low-temperature selective catalytic reduction of NO with NH_3 . The structural properties of the catalyst were characterized by FE-SEM, TEM, XRD, BET, XPS, H_2 -TPR and NH_3 -TPD analyses, and the performance of the low-temperature NH_3 -SCR was also tested. The results show that the catalyst with a molar ratio of $Pr/Mn = 0.3$ exhibited the highest NO conversion at nearly 99% at 120 °C and NO conversion greater than 90% over the temperature range of 100–240 °C. Also, the $\text{MnO}_x@PrO_x$ catalyst presented desirable SO_2 and H_2O resistance in 100 ppm SO_2 and 10 vol% H_2O at the space velocity of 40 000 h^{-1} and a testing time of 3 h test at 160 °C. The excellent low-temperature catalytic activity of the catalyst could ultimately be attributed to high concentrations of Mn^{4+} and adsorbed oxygen species on the catalyst surface, suitable Lewis acidic surface properties, and good reducing ability. Additionally, the enhanced SO_2 and H_2O resistance of the catalyst was primarily ascribed to its unique core–shell structure which prevented the MnO_x core from being sulfated.

 Received 21st January 2020
 Accepted 2nd March 2020

DOI: 10.1039/d0ra00668h

rsc.li/rsc-advances

1 Introduction

The selective catalytic reduction of NO with NH_3 (NH_3 -SCR) is considered to be the most effective and widely applied technology for eliminating NO_x from stationary sources.^{1–3} Low-temperature NH_3 -SCR, which can be placed downstream of a desulfurization tower and electrostatic precipitation in a power generation system, has gained increasing attention in recent years due to improved SCR economics.⁴ Abundant investigations have been carried out, and have made great progress in low-temperature NH_3 -SCR catalysts. Many developments have been made on low-temperature NH_3 -SCR catalysts. Among the various catalyst systems, Cu-based,^{5,6} Ce-based,⁷ Fe-based,^{8,9} Zr-based,¹⁰ Mn-contained catalysts have stimulated great interest because of their oxidation–reduction properties, environmentally friendly features and excellent low-temperature activities, however a disadvantage is easy deactivation in the presence of SO_2 in the exhaust gas.

Many strategies have been proposed to overcome this problem. One strategy includes adding other metal elements modification and is considered as one of the most promising and effective methods. Wang *et al.*¹¹ reported that the co-doping with Fe and Co can effectively improve the SO_2 resistance of a Mn–Ce/ TiO_2 catalyst because the introduction of Fe and Co can prevent SO_2 diffusion to the inner layer of the catalyst. Chang *et al.*¹² proposed that the SO_2 resistance of MnO_x - CeO_2 could be enhanced by Sn doping since it creates more Lewis acid sites on the surface for the SO_2 -containing SCR reaction. Xie *et al.*¹³ demonstrated that the addition of Cr reduced the SO_2 adsorption strength on the surface of a MnCrO_x /sepiolite catalyst, thereby increasing the anti- SO_2 poisoning of the catalyst.

Among the potential additives, rare earth oxides (REOs) have been proven to possess high catalytic activity originating from their oxygen vacancies and strong surface acidities.^{14–18} Yan *et al.*¹⁸ synthesized RE-doped Mn/ASC for the low-temperature NH_3 -SCR of NO and found that the addition of RE enhanced the catalytic activity. In addition, DRIFTS result confirm that Ce doping provides more active Brønsted acid sites. Yu *et al.*¹⁹ studied the de- NO_x catalytic activity and SO_2 resistance of Ce/ Pr - MnO_x /SAPO-34 and proposed that compared with Ce, the Pr doping on the MnO_x /SAPO-34 contained more oxygen vacancies, exhibited a superior low-temperature NH_3 -SCR activity, and inhibited the formation of ammonia sulfate on the catalyst surface, which protected the active Mn sites.

^aSchool of Environment and Energy, South China University of Technology, Guangzhou Higher Education Mega Centre, Guangzhou 510006, P. R. China. E-mail: cebhuang@scut.edu.cn

^bGuangdong Provincial Key Laboratory of Atmospheric Environment and Pollution Control, South China University of Technology, Guangzhou Higher Education Mega Centre, Guangzhou 510006, P. R. China

^cThe Key Lab of Pollution Control and Ecosystem Restoration in Industry Clusters, Ministry of Education, South China University of Technology, Guangzhou Higher Education Mega Centre, Guangzhou 510006, P. R. China



Some researchers contend that the morphology and structure of the composite oxide catalysts had an impact on their resistance to SO₂ poisoning in the low-temperature SCR process.^{20–24} Generally, compared with irregular particles, catalysts with a well-designed structure typically exhibit higher functionality due to the size, shape, and interfacial effects. Therefore, considerable research has been focused on preparing SCR catalysts with a specific structure, such as hierarchical porous structures, hollow structures or a core-shell structure. In particular, core-shell structured catalysts have attracted much attention due to their unique mechanical and structural properties for the low-temperature NH₃-SCR. For instance, a MnO_x@TiO₂ core-shell nanorod catalyst was prepared by a novel two-step method, which exhibited outstanding SCR performance due to possessed abundant mesopores and a core-shell structure. These features protect the catalytic active sites from SO₂ and H₂O poisoning.² Han *et al.* designed a *meso*-TiO₂@Fe₂O₃@Al₂O₃ core-shell material using experimental and density functional theory methods and found that the strong SO₂ tolerance was attributed to the mesoporous-TiO₂ shell, and it effectively prevented the deposition of FeSO₄ and NH₄HSO₄.²⁵ Ma *et al.* synthesized a hollow structured CeO₂-MnO_x hybrid materials with a multi-shelled structure by using carbon spheres as the hard template. This hybrid material displayed superior activity and stability over traditional CeO₂-MnO_x particles, most likely attributed to the special multi-shelled structure and abundant surface active species.²⁶ Hence, the controlled fabrication of well-structured composites is of great significance for low-temperature NH₃-SCR catalysts, and the core shape, elements and shell thicknesses are key factors. The hollow, core-shell composite structure catalyst, with special isolated chambers and controllable shell structures, would be prepared according to the structural characteristics of the hollow structure and core-shell structure. To the best of our knowledge, there are a limited number of reports about the hollow, core-shell structured Mn-Pr binary oxides as catalysts for low-temperature NH₃-SCR.

In this paper, a hollow MnO_x@PrO_x core-shell structure catalyst for the low-temperature NH₃-SCR reaction was prepared using carbon spheres both as hard template and as reducing agent. The obtained catalysts were then characterized by SEM, TEM, XRD, XPS, NH₃-TPD and H₂-TPR analysis, and the NH₃-SCR reaction performance was tested to determine the physicochemical properties and structure-performance relationships.

2 Experimental

2.1 Catalyst preparation

Carbon spheres were prepared according to a typical hydrothermal method.²⁷ Typically, a 60 mL solution containing 0.5 g glucose was hydrothermally treated at 180 °C for 24 h and then cooled to room temperature naturally. After suction, filtering and washing with deionized water and absolute ethanol, the dark brown sample was dried in a vacuum oven at 80 °C for 12 h, and the templates were obtained.

The chemical process to synthesize the hollow MnO_x@PrO_x was carried out in two steps. The CSs@MnO_x was first synthesized with the following procedure. A desired amount of CSs was placed into deionized water, and then KMnO₄ was added with unceasingly stirring for 30 min. Thereafter, the mixture solution was transferred into an autoclave and maintained at 160 °C for 12 h. Until cooling to room temperature naturally, the obtained suspension was centrifuged and washed with water and absolute ethanol repeatedly. Finally, the CSs@MnO_x was obtained by drying at 80 °C for 12 h.

Second, the hollow MnO_x@PrO_x was synthesized by a chemical precipitation method. Certain amounts of CSs@MnO_x, Pr(NO₃)₃·6H₂O, and NaOH were respectively dissolved in deionized water with the molar ratios of Pr/Mn of 0.3 and Pr(NO₃)₃·6H₂O/NaOH of 0.5. Thereafter, the Pr(NO₃)₃·6H₂O and NaOH solutions were added dropwise into above solution simultaneously and heated to 85 °C under stirring for 3 h. Finally, the hollow MnO_x@PrO_x was collected, washed to neutral, dried at 80 °C for 12 h and calcined at 400 °C in air for 3 h. The hollow MnO_x could be obtained by the roasting treatment of CSs@MnO_x. The hollow MnO_x-PrO_x catalyst without a core-shell structure was prepared through a similar method for hollow MnO_x, and the only difference was that KMnO₄ and Pr(NO₃)₃·6H₂O were added together.

2.2 NH₃-SCR activity test

The NH₃-SCR activity of the solid catalyst was carried out in a fixed-bed quartz continuous flow reactor. The feed gas was composed of 0.08% NO, 0.08% NH₃, 100 ppm SO₂ (when added), 10 vol% H₂O (when added), 5.0 vol% O₂, and the balanced gas was Ar. The total flow rate was 600 mL min⁻¹, corresponding to a gas hourly space velocity (GHSV) of 40 000 h⁻¹. The NO, NO₂ and NO_x concentrations were measured using an NO-NO₂-NO_x analyzer (Thermal Scientific, model 42i-HL), and the concentration of N₂ was monitored using a gas chromatograph (GC9560, Shanghai Huaai) with a TCD and 5 A columns. The NO removal efficiency and the N₂ selectivity were obtained by the following equations:

$$\text{NO conversion(\%)} = \frac{C_{\text{NO}}^{\text{in}} - C_{\text{NO}}^{\text{out}}}{C_{\text{NO}}^{\text{in}}} \times 100 \quad (1)$$

$$\text{N}_2 \text{ selectivity(\%)} = \frac{C_{\text{NO}}^{\text{in}} + C_{\text{NH}_3}^{\text{in}} - C_{\text{NO}}^{\text{out}} - C_{\text{NH}_3}^{\text{out}} - C_{\text{NO}_2}^{\text{out}} - 2C_{\text{N}_2\text{O}}^{\text{out}}}{C_{\text{NO}}^{\text{in}} + C_{\text{NH}_3}^{\text{in}} - C_{\text{NO}}^{\text{out}} - C_{\text{NH}_3}^{\text{out}}} \times 100 \quad (2)$$

2.3 Catalyst characterization

Field emission scanning electron microscopy (FE-SEM) with an energy dispersive spectroscopy (EDS) was used to analyze the surface morphology and elemental composition of the catalysts using a ZEISS Merlin instrument. The micro-structural characterization by transmission electron microscopy (TEM) and high-resolution TEM (HRTEM) were carried out on JEM-2100 HT. Elemental mapping was conducted using an Inca Energy 200 TEM system. X-ray diffraction (XRD) was determined using a D8



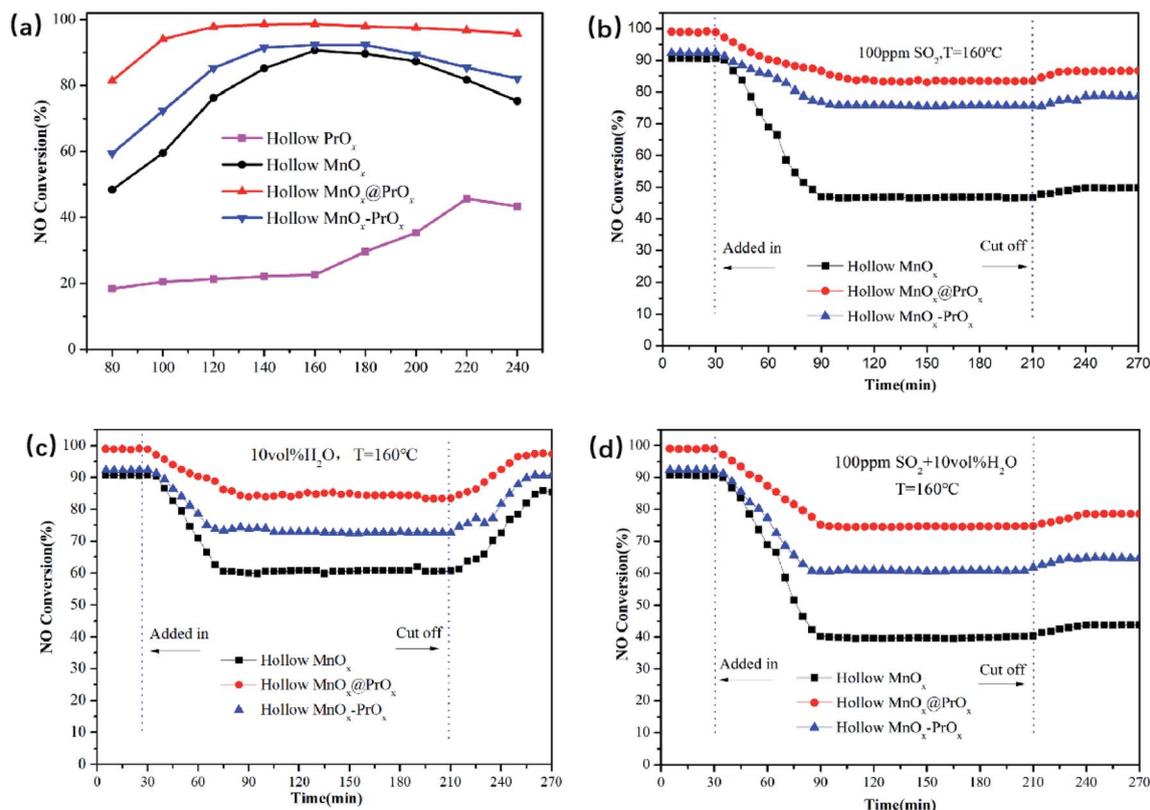


Fig. 1 NO conversion (a); SO₂ (b); H₂O (c); SO₂ + H₂O (d) tolerance test of catalysts.

Advance (Bruker) X-ray diffraction instrument with Cu K α radiation ($\lambda = 1.5406 \text{ \AA}$). X-ray photo-electron spectroscopy (XPS) analyses were carried out on an ESCALAB 250 spectrometer (Thermo Fisher Scientific, USA) equipped with Al K α X-ray radiation (1486.7 eV). H₂-TPR (10% H₂/Ar gas flow: 30 mL min⁻¹ and a heating rate of 10 °C min⁻¹) and NH₃-TPD (N₂ flow: 30 mL min⁻¹ and a heating rate of 10 °C min⁻¹) analysis were performed using a Micromeritics Auto ChemII 2920 instrument.

3 Results and discussion

3.1 Catalytic performance for the low-temperature NH₃-SCR

The NH₃-SCR catalytic performance of the hollow PrO_x, hollow MnO_x, hollow MnO_x@PrO_x and hollow MnO_x-PrO_x were shown in Fig. 1a. It could be seen from Fig. 1a that the NO conversion of the MnO_x-containing samples increased with increasing reaction temperature and then decreased, exhibiting different activated temperature windows. Comparatively, the hollow PrO_x

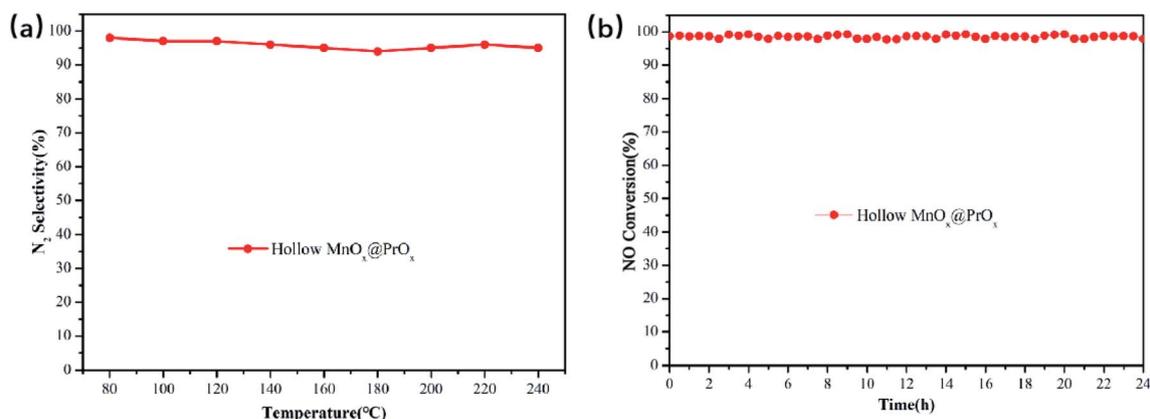


Fig. 2 N₂ selectivity (a) and stability test (b) of hollow MnO_x@PrO_x.



catalyst basically had no catalytic activity at low temperature, when the reaction temperature greater than 160 °C, and the NO conversion rate began to gradually increase and reached the maximum conversion rate about 45% at 220 °C. Comparing the four catalysts, the hollow $\text{MnO}_x@PrO_x$ catalyst exhibited superior low-temperature catalytic activity, achieving 97.1% of NO conversion at 100 °C, while the hollow PrO_x , hollow MnO_x and hollow MnO_x-PrO_x were only 21.3%, 59.5%, and 72.4%, respectively. In addition, the hollow $\text{MnO}_x@PrO_x$ catalyst displayed more than 90% NO conversion over a wider temperature range of 100–240 °C, while the other catalysts had narrow temperature windows. N_2 selectivity tests (Fig. 2a) and stability tests (Fig. 2b) were also performed and the hollow $\text{MnO}_x@PrO_x$ consistently exhibited excellent catalytic activity, high N_2 selectivity and high stability. In the whole reaction temperature range of 80–240 °C, N_2 selectivity was above 95%, and NO conversion was maintained at 97% over the 24 h stability test at 160 °C. It could be deduced that the core-shell structure promotes the synergistic effect between the MnO_x core and PrO_x shell, and enhanced catalytic activity.

The effects of SO_2 and H_2O on the low-temperature SCR activity of catalysts are shown in Fig. 1(b–d). Fig. 1b shows the NO conversion for the hollow MnO_x , hollow $\text{MnO}_x@PrO_x$ and hollow MnO_x-PrO_x catalysts when 100 ppm SO_2 was added at 160 °C. NO conversion decreased upon the addition of SO_2 . The hollow $\text{MnO}_x@PrO_x$ exhibited superior resistance to SO_2 poisoning, and the NO conversion was maintained at over 83.4% after a 3 h test, while the NO conversion of hollow MnO_x-PrO_x decreased from 92.3% to 75.5%. And the hollow MnO_x catalyst exhibited a more obvious poisoning and the NO conversion decreased from 90.7% to 46.3%. Furthermore, when SO_2 steam was cut off, the NO conversion for the catalysts could be partly restored to 86.6%, 78.7% and 49.7%, respectively. As displayed in Fig. 1c, the H_2O

resistance of the catalysts was tested using 10 vol% H_2O at 160 °C. A decrease in NO conversion from 90.6% to less than 60% for the hollow MnO_x catalyst was detected. In addition, the NO conversions of hollow $\text{MnO}_x@PrO_x$ and hollow MnO_x-PrO_x declined as well but still remained at around 84% and 73%, respectively, for the next three hours. Additionally, it is worth noting that the NO conversion with the catalysts almost recovered to its original level when H_2O was completely removed, indicating that the inhibitory effect of H_2O are reversible. According to the results shown in Fig. 1d, when 100 ppm SO_2 and 10 vol% H_2O were both introduced into the reaction system, the NO conversions of the catalysts were lower than in the presence of either SO_2 or H_2O alone. This was especially seen using the hollow MnO_x catalyst, which exhibited relatively faster deactivation with NO conversion decreasing sharply from 90.5% to 39.4% within one hour. By comparison, the coexistence of SO_2 and H_2O only resulted in a 20% decrease in NO conversion for the hollow $\text{MnO}_x@PrO_x$ and a 32% decrease for hollow MnO_x-PrO_x , indicating that the introduction of Pr element could not only significantly increase the low-temperature activity of the catalysts but also enhance the SO_2 and H_2O resistance of the catalysts. The excellent poisoning resistance of the hollow $\text{MnO}_x@PrO_x$ catalyst could be attributed to the protective effect of the PrO_x shell, which could first react with SO_2 and restrain the formation of manganese sulfate. Compared with other catalytic systems,^{28–30} the poisoning resistance of the hollow $\text{MnO}_x@PrO_x$ catalyst was relatively better than the other tested catalysts.

3.2 Structural characterization of catalysts

3.2.1 FE-SEM and TEM analysis. The morphology of the synthesized catalysts was characterized by FE-SEM (Fig. 3). Fig. 3a shows the uniform and smooth carbon spheres (CS_s),

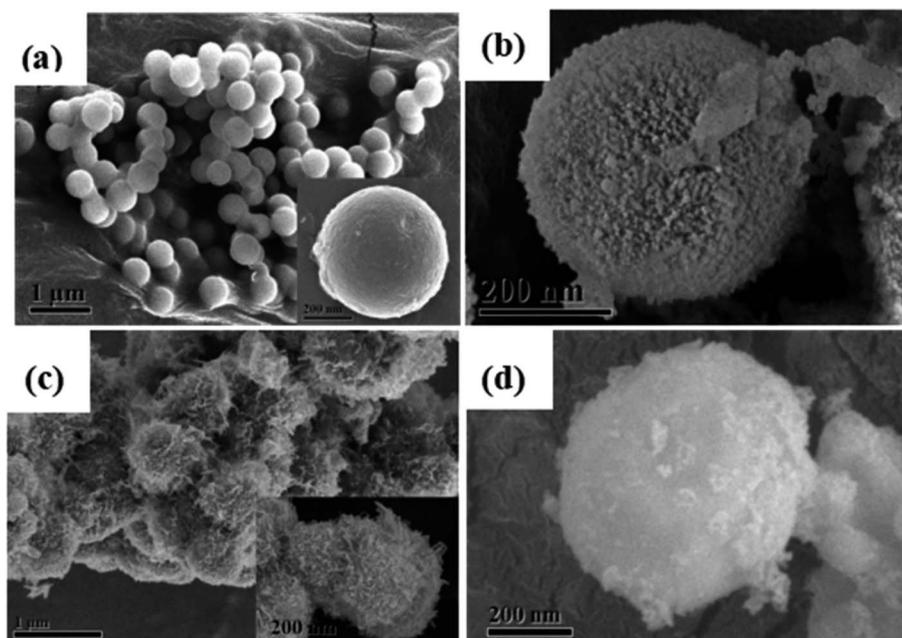


Fig. 3 Low and high-magnification FE-SEM images of CS_s (a); hollow MnO_x (b); hollow $\text{MnO}_x@PrO_x$ (c) and hollow MnO_x-PrO_x (d).



which served as both the sacrificial templates and as reducing agents. After the oxidation–reduction reaction between the KMnO_4 solution and CS_s , MnO_x particles were grown *in situ* on the CS_s surface (Fig. 3b), and maintained their spherical structure. As shown in Fig. 3c, the hollow $\text{MnO}_x@PrO_x$ catalyst was comprised of uniform spheres that were fully coated by the 1D nanosheets, and exhibited an urchin-like structure. The morphology of the hollow MnO_x-PrO_x was wrinkled when accompanied with combustion of CS_s during calcination but almost retained its original morphology (Fig. 3d).

The structural information of the catalysts were further investigated by TEM and HRTEM (Fig. 4). Fig. 4a and d revealed that the hollow $\text{MnO}_x@PrO_x$ catalyst exhibited an apparent interface between the hollow core and shell, indicating the typical features of a hollow core–shell architecture. The hollow core was about 40 nm in thickness with a 400 nm cavity and the nanosheet shell layer was about 60 nm in thickness. In addition, the TEM images of the hollow MnO_x (Fig. 4c and f) and hollow MnO_x-PrO_x (Fig. 4g and h) displayed visibly hollow structures with shell layers of about 40 nm and 100 nm in

thickness, respectively. The TEM images were in agreement with the FE-SEM images, and the *d*-spacing value was determined from the HR-TEM images and identified in the corresponding crystals. As shown in Fig. 4b and e, the highly crystalline lattice fringes with an inter-fringe spacing of 0.69 nm and 0.27 nm corresponded to the (110) plane of $\alpha\text{-MnO}_2$ (ref. 31) and the (222) plane of Mn_2O_3 .³² Lattice fringes with a spacing of 0.28 nm, 0.38 nm and 0.31 nm were indexed to the Pr_2O_3 (402), (202) planes^{33,34} and the PrO_2 (111) plane,³⁵ respectively, indicating that the hollow MnO_x nanospheres were coated by a shell of PrO_x nanosheets. However, a hollow mixed oxide was observed in the hollow MnO_x-PrO_x (Fig. 4i). Ma *et al.*²⁶ suggested that the homogeneous elemental distribution was favorable to the synergistic effects between elements, indicating that there existed intimate interactions between MnO_x and PrO_x .

The composition and distribution of the corresponding elements in the hollow $\text{MnO}_x@PrO_x$ were evaluated by EDS and elemental mapping. EDS analysis in Fig. 5a shows that the hollow $\text{MnO}_x@PrO_x$ was composed of Mn, Pr and O. In

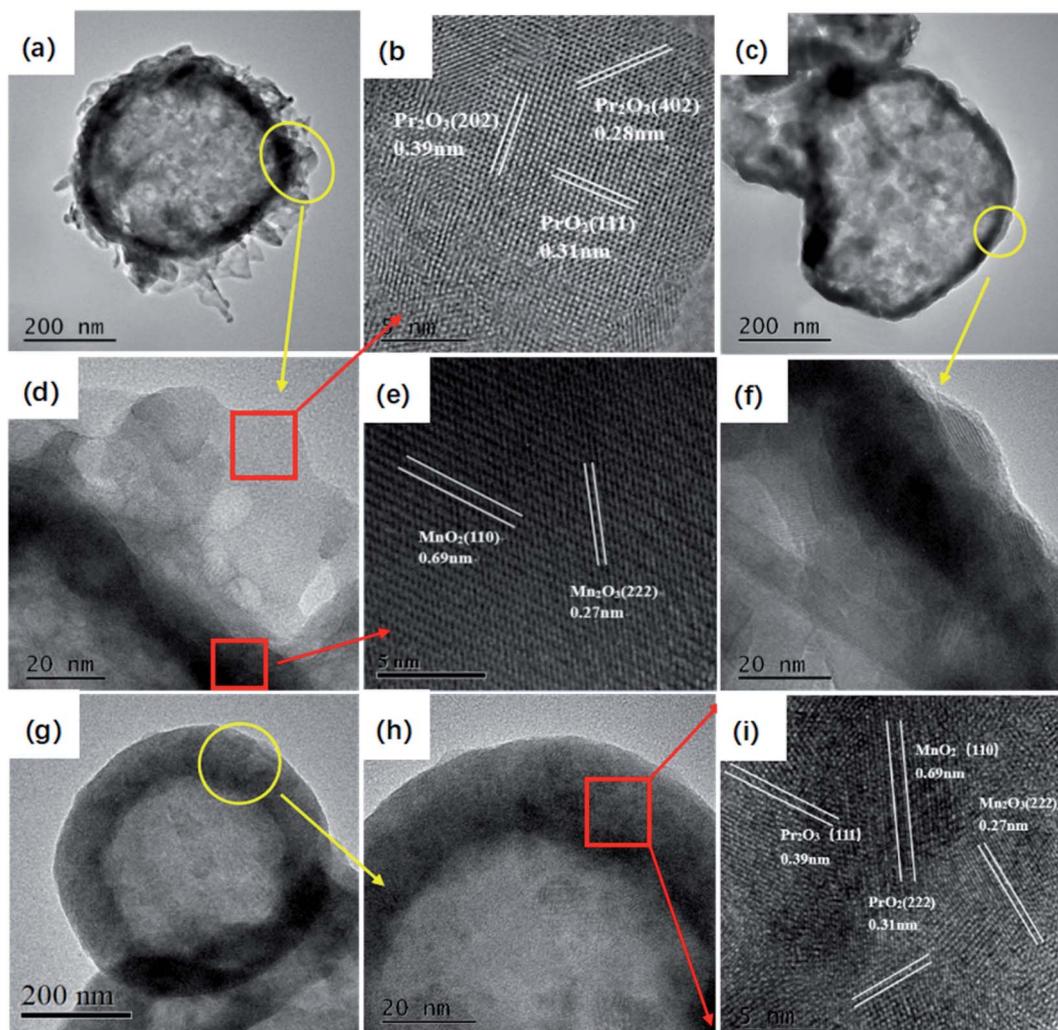


Fig. 4 TEM and FE-TEM images with different magnifications of hollow $\text{MnO}_x@PrO_x$ (a, b, d and e) and hollow MnO_x (c and f) and hollow MnO_x-PrO_x (g–i).



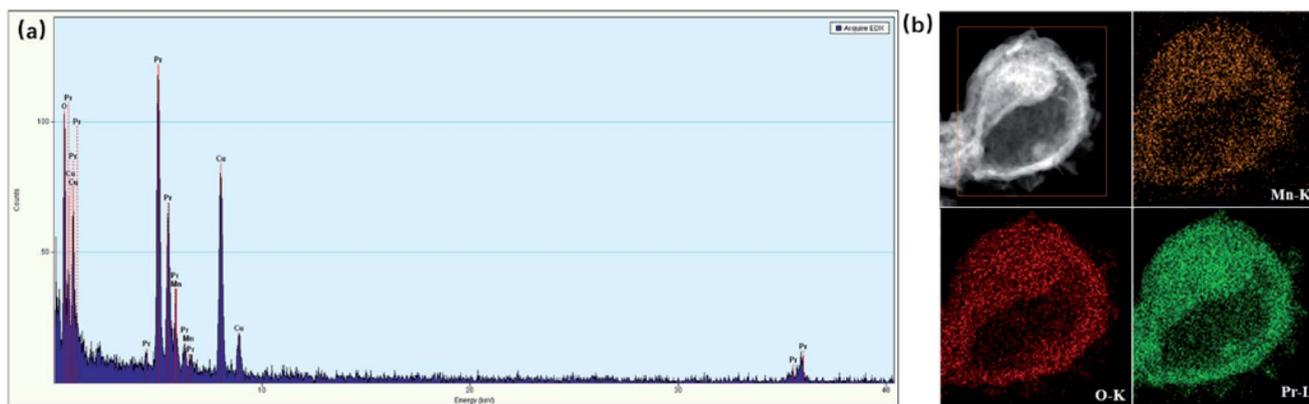


Fig. 5 EDS spectra (a) and HAADF-STEM images (b) of an individual hollow $\text{MnO}_x\text{@PrO}_x$, and its element mapping of O, Mn and Pr.

addition, the elemental map in Fig. 5b further revealed that each type of atom was uniformly distributed within the entire structure. The Pr species were located in the external layer of the hollow urchin-shaped structure, and the Mn species were observed in the interior layer. Also, the distribution range of the Pr was found to be the same as Mn, demonstrating that the PrO_x uniformly covered the MnO_x core. Based on the results above, it is reasonable to deduce that the core-shell structure catalyst could not only provide a relatively enclosed micro-environment to expose abundant active sites and enhance mass transfer, but the PrO_x shell also protected the MnO_x core from being poisoned. This contributed to an excellent $\text{SO}_2/\text{H}_2\text{O}$ -tolerance of the hollow $\text{MnO}_x\text{@PrO}_x$ catalyst.

3.2.2 XRD and BET analysis. XRD tests were carried out to determine the component and crystal phase structures of the catalysts. The crystalline structure of the active component plays an important role in its catalytic performance. Fig. 6 exhibits the typical XRD pattern of the catalysts including CSS, hollow MnO_x and hollow $\text{MnO}_x\text{@PrO}_x$. For the CSS templates, only a distinct diffraction peak at $2\theta = 24^\circ$ was detected, which was associated with the carbon material.³⁶ Interestingly, no characteristic peaks of CSS were observed in the hollow MnO_x , hollow $\text{MnO}_x\text{@PrO}_x$, or hollow $\text{MnO}_x\text{-PrO}_x$, suggesting that the sacrificial template of CSS was completely eliminated by heating at 400°C . With regard to the hollow MnO_x , the peaks at $2\theta = 12.8^\circ, 18.1^\circ, 28.8^\circ, 37.5^\circ, 41.9^\circ, 49.8^\circ, 56.4^\circ, 60.3^\circ,$ and 69.7° were attributed to MnO_2 ,³⁷ while the peaks at $2\theta = 32.9^\circ, 55.2^\circ,$ and 65.8° were assigned to Mn_2O_3 .³⁸ This phenomenon demonstrated the coexistence of different Mn species in the catalyst and that MnO_2 was the main phase. After adding the Pr species, characteristic peaks at $2\theta = 28.6^\circ, 47.6^\circ$ and $22.8^\circ, 31.1^\circ, 45.6^\circ$ were observed for the hollow $\text{MnO}_x\text{@PrO}_x$ and hollow $\text{MnO}_x\text{-PrO}_x$, which were related to the (110), (220) planes of PrO_2 and the (202), (402), (503) planes of Pr_2O_3 , respectively. The XRD results were also in agreement with the HRTEM images. Also, the diffraction peaks of both catalysts shifted slightly to higher angles, which was attributed to that the manganese ions ($\text{Mn}^{4+} = 53 \text{ \AA}, \text{Mn}^{3+} = 64.5 \text{ \AA}, \text{Mn}^{2+} = 83 \text{ \AA}$) being partly diffused into the PrO_x ($\text{Pr}^{4+} = 85 \text{ \AA}, \text{Pr}^{3+} = 99 \text{ \AA}$) lattice during the heating process, which led to lattice shrinkage.^{29,30,39-41} Additionally, as compared with the hollow MnO_x , the

characteristic XRD peaks of the MnO_2 and Mn_2O_3 were weaker and wider, which revealed that smaller mixed oxide particles with a lower degree of crystallization were formed. According to some reports,^{40,42,43} the decrease in crystallization degree led to increase of surface adsorbed oxygen, thus contributing to an improved SCR performance. The BET-specific surface areas of the catalysts were measured and are summarized in Table 1. It was reported that with a larger specific surface area and pore volume of the catalyst, the exposure of active sites increased and more reactants were adsorbed on the surfaces.³⁹ As can be seen from Table 1, after introducing Pr, the surface area and pore volume increased as follows: hollow $\text{MnO}_x\text{@PrO}_x$ ($195.31 \text{ m}^3 \text{ g}^{-1}, 0.36 \text{ cm}^3 \text{ g}^{-1}$) > hollow $\text{MnO}_x\text{-PrO}_x$ ($185.39 \text{ m}^3 \text{ g}^{-1}, 0.31 \text{ cm}^3 \text{ g}^{-1}$) > hollow MnO_x ($136.70 \text{ m}^3 \text{ g}^{-1}, 0.24 \text{ cm}^3 \text{ g}^{-1}$). This indicated that more reactants were adsorbed on the core-shell structure hollow $\text{MnO}_x\text{@PrO}_x$ catalyst leading to an increase in the SCR reactions.

3.2.3 XPS analysis. The surface properties of the catalysts also play an important role in the NH_3 -SCR reaction. Hence, the surface atom concentrations and states of the catalysts were determined by XPS (Fig. 7 and Table 1). The XPS spectrum of




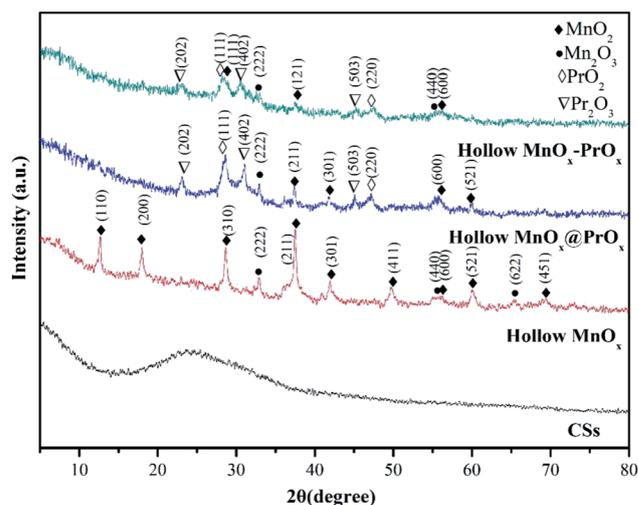


Fig. 6 XRD patterns of CSS, hollow MnO_x , hollow $\text{MnO}_x\text{@PrO}_x$ and hollow $\text{MnO}_x\text{-PrO}_x$.



Mn 2p_{3/2} is shown in Fig. 7a and could be divided into three peaks: Mn²⁺ (640.2–640.8 eV), Mn³⁺ (641.2–641.5 eV) and Mn⁴⁺ (642.5–643.0 eV).^{44,45} The spectra of the hollow MnO_x@PrO_x and the hollow MnO_x-PrO_x were slightly shifted to lower binding energies. Similar results have been obtained by Ma *et al.*²⁶ and Chang *et al.*,⁴⁶ demonstrating that the chemical environment of Mn was different from the hollow MnO_x, suggesting that there was an interaction between the MnO_x species and the PrO_x species given in the following reactions:



As listed in Table 1, among the three catalysts, the hollow MnO_x@PrO_x possessed the highest surface molar concentration of Mn⁴⁺ (58.3%), indicating that the PrO_x shell might have enriched the surface concentration of the Mn⁴⁺ species. It was confirmed that the Mn⁴⁺ species and their oxidation–reduction processes were in favor of the low-temperature NH₃-SCR reaction.^{44,47–49} As a result, with more Mn⁴⁺ species, the low-temperature catalytic activity of the catalyst was enhanced. Furthermore, it was worth noting that the concentrations of Mn significantly decreased after the coating with a PrO_x shell, which suggested that most of the Mn species were covered by PrO_x. In other words, PrO_x mainly deposited on the surface of catalyst, and the results were consistent with TEM.

The XPS spectrum of the Pr 3d reported in Fig. 7b shows two sets of spin–orbit multiples that were observed at binding energies of *ca.* 953.5 and 933.9 eV, which represented the 3d_{3/2} and 3d_{5/2} electrons of Pr, respectively.⁵⁰ According to He *et al.*,⁵¹ the signals at *ca.* 928.6, 933.2, 946.3, and 951.1 eV were assigned to Pr³⁺, and the signals at *ca.* 930.5, 933.9, 949.2, 953.7, and 956.8 eV to Pr⁴⁺. The characteristic features of Pr⁴⁺ at 966–968 eV could not be resolved in the figure. As reported in other studies,^{52,53} this unique peak of Pr⁴⁺ usually appears after oxidation treatment (O₂) of PrO_x within the XPS reactor chamber. The Pr⁴⁺ ions were unstable and lose electrons easily, which facilitated the process of oxygen storage and release between Pr⁴⁺ and Pr³⁺ (2PrO₂ → Pr₂O₃ + O*; Pr₂O₃ + 1/2O₂ → 2PrO₂).^{51,54} That is, the existence of Pr³⁺ in the PrO_x implied the formation of an oxygen vacancy and the ratios of Pr³⁺/(Pr³⁺ + Pr⁴⁺) (39.6%) in the hollow MnO_x@PrO_x were higher than in the

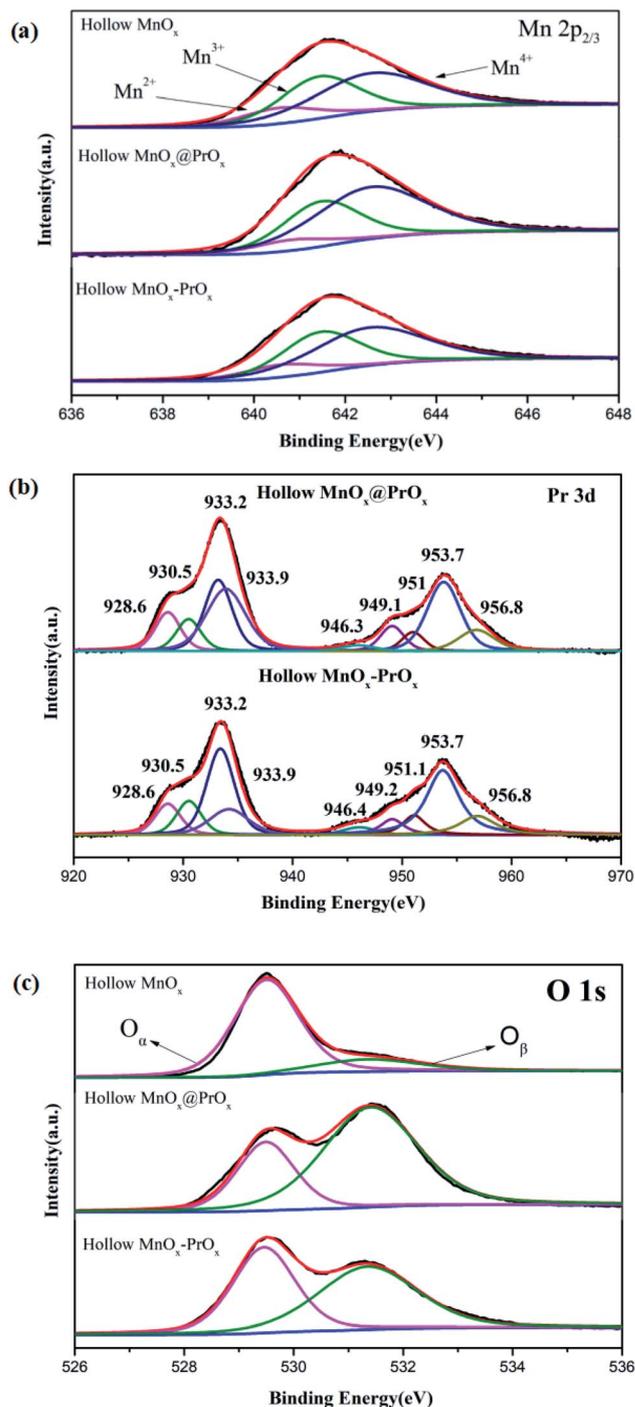


Fig. 7 XPS spectra of Mn 2p_{2/3} (a), Pr 3d (b) and O 1s (c) of the catalysts.

Table 1 BET surface area and surface atomic composition of the catalysts

Sample	Surface atomic concentration (%)			$X_{\text{Mn}}/\%$			$X_{\text{O}}/\%$		$X_{\text{Pr}}/\%$		BET (m ² g ⁻¹)	Pore volume (cm ³ g ⁻¹)
	Mn	O	Pr	Mn ⁴⁺	Mn ³⁺	Mn ²⁺	O _α	O _β	Pr ⁴⁺	Pr ³⁺		
Hollow MnO _x	39.47	60.53	—	49.01	37.02	13.97	83.05	16.95	—	—	136.70	0.24
Hollow MnO _x @PrO _x	12.62	54.19	33.19	58.27	33.24	8.49	29.7	70.3	60.4	39.6	195.31	0.36
Hollow MnO _x -PrO _x	34.58	50.19	15.23	51.1	37.3	11.6	57.36	42.64	66.4	33.6	185.39	0.31



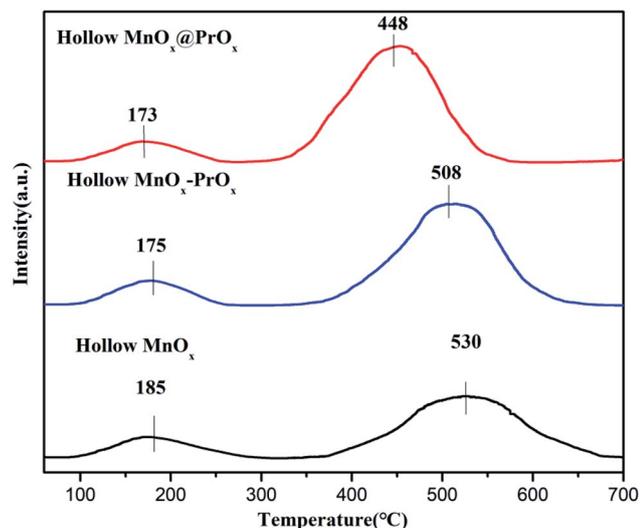


Fig. 8 NH_3 -TPD profiles of the catalysts.

hollow $\text{MnO}_x\text{-PrO}_x$ (33.6%). Therefore, it could be inferred that more oxygen vacancies were present in the hollow $\text{MnO}_x\text{@PrO}_x$ than in the hollow $\text{MnO}_x\text{-PrO}_x$.

The O 1s XPS spectrum for the catalysts were also shown in Fig. 7c. The sub-band at 531.3–532.2 eV was attributed to the surface-adsorbed oxygen species (O_β), and the sub-band at 529.2–530.0 eV was attributed to the lattice oxygen species (O_α).⁴¹ It is well known that O_β is more active than O_α , therefore the higher mobility of the O_β led to better performance in the oxidation reaction. An increase in the O_β content promoted the oxidation of NO to NO_2 and further enhanced the low-temperature NH_3 -SCR reaction through a fast pathway ($4\text{NH}_3 + 2\text{NO} + 2\text{NO}_2 \rightarrow 4\text{N}_2 + 6\text{H}_2\text{O}$).^{55,56} From Table 1, the ratio of $\text{O}_\beta/(\text{O}_\alpha + \text{O}_\beta)$ in the hollow $\text{MnO}_x\text{@PrO}_x$ (70.3%) was the highest of the three catalysts, which agrees with the XRD analysis, and could also explain the excellent low-temperature SCR activity of the hollow $\text{MnO}_x\text{@PrO}_x$ catalyst.

3.2.4 NH_3 -TPD analysis. NH_3 -TPD was carried out to evaluate the amount of the acid sites and the acid strength of the prepared catalysts (Fig. 8 and Table 2). The TPD profile of the catalysts presented two broad desorption peaks in the temperature ranges of 100–300 °C and 400–700 °C. It was generally believed that the desorption peaks before 400 °C were ascribed to the weak adsorption of the NH_3 at the Brønsted acid sites, while the desorption peaks above 400 °C were ascribed to the strong adsorption of the NH_3 at the Lewis acid sites.⁵⁷ Moreover,

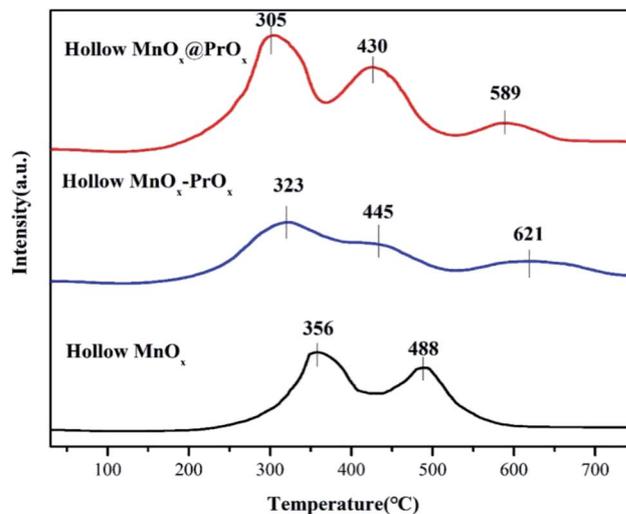


Fig. 9 H_2 -TPR profiles of the catalysts.

the positions of the desorption peaks were related to the acid strength and the areas of desorption peaks were related to the amount of acid sites.³ As shown in Fig. 8, all catalysts exhibited less Brønsted acid sites but much more Lewis acid sites. In addition, in the higher temperature range, the hollow $\text{MnO}_x\text{@PrO}_x$ catalyst possessed the largest desorption area and the lowest desorption temperature at the Lewis acid sites, indicating that there was a sufficient number of Lewis acid sites with suitable acid strength on its surface. Studies show that the appropriate acid strength and number of sites are conducive to the adsorption-activation of NH_3 on the catalyst surface.⁵⁸ Moreover, the total number of acid sites for the catalysts were roughly calculated from the NH_3 -TPD, which was listed in Table 2. The acid strength sequence of the catalysts was: hollow $\text{MnO}_x\text{@PrO}_x >$ hollow $\text{MnO}_x\text{-PrO}_x >$ hollow MnO_x . Based on the results, it was concluded that the hollow $\text{MnO}_x\text{@PrO}_x$ catalyst contained a highly effective specific surface area due to its architecture, more acid sites could be exposed, and the catalyst exhibited enhanced adsorption ability of NH_3 , giving the same results as the BET analysis.

3.2.5 H_2 -TPR analysis. The H_2 -TPR test was performed to better understand the redox properties of the catalysts and the results were shown in Fig. 9. It was seen that the hollow MnO_x exhibited two reduction peaks located at 356 and 488 °C, corresponding to the consecutive reduction processes of $\text{MnO}_2\text{-Mn}_2\text{O}_3$ or $\text{Mn}_3\text{O}_4\text{-MnO}$.^{59–63} Three reduction peaks were

Table 2 The surface acidic properties of the catalysts

Sample	Peak temperature (°C)		Acid amount (mmol g^{-1})		Total acid amount (mmol g^{-1})
	T_I	T_{II}	S_I	S_{II}	
Hollow $\text{MnO}_x\text{@PrO}_x$	173	448	0.141	1.345	1.486
Hollow $\text{MnO}_x\text{-PrO}_x$	175	508	0.13	1.047	1.177
Hollow MnO_x	185	530	0.123	0.726	0.849



Table 3 The reducibility of the catalysts

Sample	Peak temperature (°C)			H ₂ consumption (mmol g ⁻¹)			Total H ₂ consumption (mmol g ⁻¹)
	T _I	T _{II}	T _{III}	S _I	S _{II}	S _{III}	
Hollow MnO _x @PrO _x	305	430	589	0.875	0.375	0.0838	1.3338
Hollow MnO _x -PrO _x	323	445	621	0.6788	0.211	0.086	0.9758
Hollow MnO _x	356	488	—	0.629	0.202	—	0.831

observed for the hollow MnO_x@PrO_x and hollow MnO_x-PrO_x with the two peaks at higher temperatures coming from the conversion of Pr⁴⁺ to Pr³⁺, or the reduction reaction between Mn⁴⁺/Mn³⁺ and Pr⁴⁺/Pr³⁺.⁶⁴ Specifically, the first two peaks were notably shifted to lower temperatures for both catalysts, indicating that the reduction capacity of the catalysts were improved and easier to reduce at low temperatures. In addition, the total consumption of H₂ for the hollow MnO_x@PrO_x remarkably increased over the hollow MnO_x, as illustrated in Table 3. This implied that the addition of PrO_x generated more reducing agents on the catalyst surface, which is consistent with the XPS results showing a higher reducing ability. The increased reducibility of the hollow MnO_x@PrO_x over the hollow MnO_x-PrO_x catalysts further proved that the special core-shell structure of the catalyst was the main reason for the excellent reducibility.

4 Conclusion

In summary, we have successfully fabricated a hollow MnO_x@PrO_x core-shell nanohybrid as a high-performance low-temperature NH₃-SCR de-NO_x catalyst by using a facile two-step method. The hollow MnO_x@PrO_x nanohybrid displayed excellent low-temperature NH₃-SCR activity with a maximum NO conversion of 99% at 120 °C with a space velocity of 40 000 h⁻¹. It also maintained a NO conversion above 90% within the broad temperature window of 100–240 °C. This favorable catalytic behavior was mainly due to the abundant content of Mn⁴⁺ and O_β species, uniform distribution of Mn and Pr species, and intimate interaction between MnO_x and PrO_x which brought about plentiful Lewis acid sites and excellent reducibility. Besides the excellent catalytic activity, the hollow MnO_x@PrO_x catalyst consistently exhibited superior SO₂ and H₂O tolerance, which could be attributed to the special core-shell structure of the catalyst. The protection from the PrO_x shell minimized the exposure of the hollow MnO_x core surface active sites to SO₂ or H₂O, resulting in high stability and an improved anti-poisoning performance.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The project is financially supported by the National Natural Science Foundation of China (NSFC-51478191).

References

- 1 T. Ryu, N. H. Ahn, S. Seo, J. Cho, H. Kim, D. Jo, G. T. Park, P. S. Kim, C. H. Kim, E. L. Bruce, P. A. Wright, I. S. Nam and S. B. Hong, Fully Copper-Exchanged High-Silica LTA Zeolites as Unrivaled Hydrothermally Stable NH₃-SCR Catalysts, *Angew. Chem., Int. Ed. Engl.*, 2017, **56**, 3256–3260.
- 2 Z. Sheng, D. Ma, D. Yu, X. Xiao, B. Huang, L. Yang and S. Wang, Synthesis of novel MnO_x@TiO₂ core-shell nanorod catalyst for low-temperature NH₃-selective catalytic reduction of NO_x with enhanced SO₂ tolerance, *Chin. J. Catal.*, 2018, **39**, 821–830.
- 3 B. Thirupathi and P. G. Smirniotis, Nickel-doped Mn/TiO₂ as an efficient catalyst for the low-temperature SCR of NO with NH₃: catalytic evaluation and characterizations, *J. Catal.*, 2012, **288**, 74–83.
- 4 S. Li, B. Huang and C. Yu, A CeO₂-MnO_x core-shell catalyst for low-temperature NH₃-SCR of NO, *Catal. Commun.*, 2017, **98**, 47–51.
- 5 Y. Cao, D. Fan, L. Sun, M. Yang, L. Cao, T. Sun, S. Xu, P. Tian and Z. Liu, The self-protection effect of reactant gas on the moisture stability of CuSAPO-34 catalyst for NH₃-SCR, *Chem. Eng. J.*, 2019, **374**, 832–839.
- 6 H. I. Hamoud, V. Valtchev and M. Daturi, Selective catalytic reduction of NO_x over Cu- and Fe-exchanged zeolites and their mechanical mixture, *Appl. Catal., B*, 2019, **250**, 419–428.
- 7 D. Wang, Y. Peng, Q. Yang, F. Hu, J. Li and J. Crittenden, NH₃-SCR performance of WO₃ blanketed CeO₂ with different morphology: balance of surface reducibility and acidity, *Catal. Today*, 2019, **332**, 42–48.
- 8 L. Peng, Z. Li, J. Cui, C. Geng, Y. Kang, C. Zhang and C. Yang, N-doped graphene/CoFe₂O₄ catalysts for the selective catalytic reduction of NO_x by NH₃, *RSC Adv.*, 2019, **9**, 15791.
- 9 N. Zhu, Z. Lian, Y. Zhang, W. Shan and H. He, Improvement of low-temperature catalytic activity over hierarchical Fe-beta catalysts for selective catalytic reduction of NO with NH₃, *Chin. Chem. Lett.*, 2019, **30**, 867–870.
- 10 S. Liu, H. Wang, Y. Wei, R. Zhang and S. Royer, Morphology-Oriented ZrO₂-Supported Vanadium Oxide for the NH₃-SCR Process: Importance of Structural and Textural Properties, *ACS Appl. Mater. Interfaces*, 2019, **11**, 22240–22254.
- 11 F. Wang, B. Shen, S. Zhu and Z. Wang, Promotion of Fe and Co doped Mn-Ce/TiO₂ catalysts for low temperature NH₃-SCR with SO₂ tolerance, *Fuel*, 2019, **249**, 54–60.
- 12 H. Chang, J. Li, X. Chen, L. Ma, S. Yang, J. W. Schwank and J. Hao, Effect of Sn on MnO_x-CeO₂ catalyst for SCR of NO_x by



- ammonia: enhancement of activity and remarkable resistance to SO₂, *Catal. Commun.*, 2012, **27**, 54–57.
- 13 A. Xie, Y. Tang, X. Huang, X. Jin, P. Gu, S. Luo, C. Yao and X. Li, Three-dimensional nanoflower MnCrO/sepiolite catalyst with increased SO₂ resistance for NH₃-SCR at low temperature, *Chem. Eng. J.*, 2019, **370**, 897–905.
 - 14 U. Hennings and R. Reimert, Investigation of the structure and the redox behavior of gadolinium doped ceria to select a suitable composition for use as catalyst support in the steam reforming of natural gas, *Appl. Catal., A*, 2007, **325**, 41–49.
 - 15 B. Jiang, B. Deng, Z. Zhang, Z. Wu, X. Tang, S. Yao and H. Lu, Effect of Zr Addition on the Low-Temperature SCR Activity and SO₂ Tolerance of Fe–Mn/Ti Catalysts, *J. Phys. Chem. C*, 2014, **118**, 14866–14875.
 - 16 P. Maitarad, J. Han, D. Zhang, L. Shi, S. Namuangruk and T. Rungrotmongkol, Structure–Activity Relationships of NiO on CeO₂ Nanorods for the Selective Catalytic Reduction of NO with NH₃: Experimental and DFT Studies, *J. Phys. Chem. C*, 2014, **118**, 9612–9620.
 - 17 L. Xiangwen, Z. Kebin, W. Lei, W. Baoyi and L. Yadong, Oxygen vacancy clusters promoting reducibility and activity of ceria nanorods, *J. Am. Chem. Soc.*, 2009, **131**, 3140–3141.
 - 18 Z. Yan, Y. Qu, L. Liu, X. Ge, J. Yang, L. Wei, T. Yang and X. Wang, Promotional effect of rare earth-doped manganese oxides supported on activated semi-coke for selective catalytic reduction of NO with NH₃, *Environ. Sci. Pollut. Res. Int.*, 2017, **24**, 24473–24484.
 - 19 C. Yu, B. Huang, L. Dong, F. Chen, Y. Yang, Y. Fan, Y. Yang, X. Liu and X. Wang, Effect of Pr/Ce addition on the catalytic performance and SO₂ resistance of highly dispersed MnO_x/SAPO-34 catalyst for NH₃-SCR at low temperature, *Chem. Eng. J.*, 2017, **316**, 1059–1068.
 - 20 R.-t. Guo, Q.-l. Chen, H.-l. Ding, Q.-s. Wang, W.-g. Pan, N.-z. Yang and C.-z. Lu, Preparation and characterization of CeO_x@MnO_x core–shell structure catalyst for catalytic oxidation of NO, *Catal. Commun.*, 2015, **69**, 165–169.
 - 21 X. W. Lou, L. A. Archer and Z. Yang, Hollow Micro-/Nanostructures: Synthesis and Applications, *Adv. Mater.*, 2008, **20**, 3987–4019.
 - 22 J. Yu, F. Guo, Y. Wang, J. Zhu, Y. Liu, F. Su, S. Gao and G. Xu, Sulfur poisoning resistant mesoporous Mn-base catalyst for low-temperature SCR of NO with NH₃, *Appl. Catal., B*, 2010, **95**, 160–168.
 - 23 S. Zhan, M. Qiu, S. Yang, D. Zhu, H. Yu and Y. Li, Facile preparation of MnO₂ doped Fe₂O₃ hollow nanofibers for low temperature SCR of NO with NH₃, *J. Mater. Chem. A*, 2014, **2**, 20486–20493.
 - 24 L. Zhang, L. Shi, L. Huang, J. Zhang, R. Gao and D. Zhang, Rational Design of High-Performance DeNO_x Catalysts Based on Mn_xCo_{3–x}O₄ Nanocages Derived from Metal–Organic Frameworks, *ACS Catal.*, 2014, **4**, 1753–1763.
 - 25 L. Han, M. Gao, J. Y. Hasegawa, S. Li, Y. Shen, H. Li, L. Shi and D. Zhang, SO₂-Tolerant Selective Catalytic Reduction of NO_x over Meso-TiO₂@Fe₂O₃@Al₂O₃ Metal-Based Monolith Catalysts, *Environ. Sci. Technol.*, 2019, **53**, 6462–6473.
 - 26 K. Ma, W. Zou, L. Zhang, L. Li, S. Yu, C. Tang, F. Gao and L. Dong, Construction of hybrid multi-shell hollow structured CeO₂–MnO_x materials for selective catalytic reduction of NO with NH₃, *RSC Adv.*, 2017, **7**, 5989–5999.
 - 27 X. Sun and Y. Li, Colloidal carbon spheres and their core/shell structures with noble-metal nanoparticles, *Angew. Chem., Int. Ed. Engl.*, 2004, **43**, 597–601.
 - 28 W. Li, C. Zhang, X. Li, P. Tan, A. Zhou, Q. Fang and G. Chen, Ho-modified Mn–Ce/TiO₂ for low-temperature SCR of NO with NH₃: evaluation and characterization, *Chin. J. Catal.*, 2018, **39**, 1653–1663.
 - 29 X. Yao, J. Cao, L. Chen, K. Kang, Y. Chen, M. Tian and F. Yang, Doping effect of cations (Zr⁴⁺, Al³⁺, and Si⁴⁺) on MnO/CeO₂ nano-rod catalyst for NH₃-SCR reaction at low temperature, *Chin. J. Catal.*, 2019, **40**, 733–743.
 - 30 X. Yao, L. Chen, J. Cao, Y. Chen, M. Tian, F. Yang, J. Sun, C. Tang and L. Dong, Enhancing the deNO performance of MnO/CeO₂-ZrO₂ nanorod catalyst for low-temperature NH₃-SCR by TiO₂ modification, *Chem. Eng. J.*, 2019, **369**, 46–56.
 - 31 S. Liang, F. Teng, G. Bulgan, R. Zong and Y. Zhu, Effect of Phase Structure of MnO₂ Nanorod Catalyst on the Activity for CO Oxidation, *J. Phys. Chem. C*, 2010, **112**, 5307–5315.
 - 32 J. Xu, Y. Sun, M. Lu, L. Wang, J. Zhang, J. Qian and E. J. Kim, Fabrication of porous Mn₂O₃ microsheet arrays on nickel foam as high-rate electrodes for supercapacitors, *J. Alloys Compd.*, 2017, **717**, 108–115.
 - 33 M. F. Gazulla, M. J. Ventura, C. Andreu, J. Gilabert, M. Orduña and M. Rodrigo, Praseodymium oxides. Complete characterization by determining oxygen content, *Microchem. J.*, 2019, **148**, 291–298.
 - 34 P. Monica and M. Kakihana, Praseodymium oxide formation by thermal decomposition of a praseodymium complex, *Solid State Ionics*, 2001, **141–142**, 265–272.
 - 35 B. Mutharani, P. Ranganathan, S. M. Chen and P. Sireesha, Ultrasound-induced radicals initiated the formation of inorganic-organic Pr₂O₃/polystyrene hybrid composite for electro-oxidative determination of chemotherapeutic drug methotrexate, *Ultrason. Sonochem.*, 2019, **56**, 410–421.
 - 36 H. Wang, Z. Zhang, C. Dong, G. Chen, Y. Wang and H. Guan, Carbon spheres@MnO₂ core-shell nanocomposites with enhanced dielectric properties for electromagnetic shielding, *Sci. Rep.*, 2017, **7**, 15841.
 - 37 K. Lei, L. Cong, X. Fu, F. Cheng and J. Chen, Stirring-assisted hydrothermal synthesis of ultralong α-MnO₂ nanowires for oxygen reduction reaction, *Inorg. Chem. Front.*, 2016, **3**, 928–933.
 - 38 Y.-C. Zhang, J.-T. Li, Z.-G. Wu, L. Huang and S.-G. Sun, Synthesis of hierarchical spindle-like Mn₂O₃ for lithium ion batteries with enhanced lithium storage properties, *J. Alloys Compd.*, 2017, **721**, 229–235.
 - 39 T. Du, H. Qu, Q. Liu, Q. Zhong and W. Ma, Synthesis, activity and hydrophobicity of Fe-ZSM-5@silicalite-1 for NH₃-SCR, *Chem. Eng. J.*, 2015, **262**, 1199–1207.
 - 40 B. Shen, F. Wang and T. Liu, Homogeneous MnO–CeO₂ pellets prepared by a one-step hydrolysis process for low-temperature NH₃-SCR, *Powder Technol.*, 2014, **253**, 152–157.



- 41 J. Wang, Z. Yan, L. Liu, Y. Zhang, Z. Zhang and X. Wang, Low-temperature SCR of NO with NH₃ over activated semi-coke composite-supported rare earth oxides, *Appl. Surf. Sci.*, 2014, **309**, 1–10.
- 42 F. Gao, X. Tang, H. Yi, J. Li, S. Zhao, J. Wang, C. Chu and C. Li, Promotional mechanisms of activity and SO₂ tolerance of Co- or Ni-doped MnO_x-CeO₂ catalysts for SCR of NO_x with NH₃ at low temperature, *Chem. Eng. J.*, 2017, **317**, 20–31.
- 43 Z. Liu, Y. Yi, S. Zhang, T. Zhu, J. Zhu and J. Wang, Selective catalytic reduction of NO_x with NH₃ over Mn-Ce mixed oxide catalyst at low temperatures, *Catal. Today*, 2013, **216**, 76–81.
- 44 Y. Su, B. Fan, L. Wang, Y. Liu, B. Huang, M. Fu, L. Chen and D. Ye, MnO_x supported on carbon nanotubes by different methods for the SCR of NO with NH₃, *Catal. Today*, 2013, **201**, 115–121.
- 45 L. Wang, B. Huang, Y. Su, G. Zhou, K. Wang, H. Luo and D. Ye, Manganese oxides supported on multi-walled carbon nanotubes for selective catalytic reduction of NO with NH₃: catalytic activity and characterization, *Chem. Eng. J.*, 2012, **192**, 232–241.
- 46 H. Chang, T. Zhang, H. Dang, X. Chen, Y. You, J. W. Schwank and J. Li, Fe₂O₃@SiTi core-shell catalyst for the selective catalytic reduction of NO_x with NH₃: activity improvement and HCl tolerance, *Catal. Sci. Technol.*, 2018, **8**, 3313–3320.
- 47 Y. Chao, L. X. H. BiChun and W. YouMing, Structural Properties and Low-Temperature SCR Activity of Zirconium-Modified MnO_x/MWCNTs Catalysts, *Acta Phys.-Chim. Sin.*, 2014, **30**, 1895–1920.
- 48 X. Du, C. Li, L. Zhao, J. Zhang, L. Gao, J. Sheng, Y. Yi, J. Chen and G. Zeng, Promotional removal of HCHO from simulated flue gas over Mn-Fe oxides modified activated coke, *Appl. Catal., B*, 2018, **232**, 37–48.
- 49 B. Zhao, H. Yi, X. Tang, Q. Li, D. Liu and F. Gao, Using CuO-MnO_x/AC-H as catalyst for simultaneous removal of Hg degrees and NO from coal-fired flue gas, *J. Hazard. Mater.*, 2019, **364**, 700–709.
- 50 F. Liu, H. He, Y. Ding and C. Zhang, Effect of manganese substitution on the structure and activity of iron titanate catalyst for the selective catalytic reduction of NO with NH₃, *Appl. Catal., B*, 2009, **93**, 194–204.
- 51 H. He, H. X. Dai, K. W. Wong and C. T. Au, RE_{0.6}Zr_{0.4-x}Y_xO₂ (RE = Ce, Pr; x = 0, 0.05) solid solutions: an investigation on defective structure, oxygen mobility, oxygen storage capacity, and redox properties, *Appl. Catal., A*, 2003, **251**, 61–74.
- 52 C. K. Narula, L. P. Haack, W. Chun, H.-W. Jen and G. W. Graham, Single-Phase PrOy-ZrO₂ Materials and Their Oxygen Storage Capacity: A Comparison with Single-Phase CeO₂-ZrO₂, PrOy-CeO₂, and PrOy-CeO₂-ZrO₂ Materials, *J. Phys. Chem. B*, 1999, **103**, 3634–3639.
- 53 E. Poggio-Fraccari, G. Baronetti and F. Mariño, Pr³⁺ surface fraction in CePr mixed oxides determined by XPS analysis, *J. Electron Spectrosc. Relat. Phenom.*, 2018, **222**, 1–4.
- 54 Z. Song, W. Liu, H. Nishiguchi, A. Takami, K. Nagaoka and Y. Takita, The Pr promotion effect on oxygen storage capacity of Ce-Pr oxides studied using a TAP reactor, *Appl. Catal., A*, 2007, **329**, 86–92.
- 55 X. Lu, C. Song, S. Jia, Z. Tong, X. Tang and Y. Teng, Low-temperature selective catalytic reduction of NO_x with NH₃ over cerium and manganese oxides supported on TiO₂-graphene, *Chem. Eng. J.*, 2015, **260**, 776–784.
- 56 L. Zhang, D. Zhang, J. Zhang, S. Cai, C. Fang, L. Huang, H. Li, R. Gao and L. Shi, Design of meso-TiO₂@MnO(x)-CeO(x)/CNTs with a core-shell structure as DeNO(x) catalysts: promotion of activity, stability and SO₂-tolerance, *Nanoscale*, 2013, **5**, 9821–9829.
- 57 Z. Fan, J.-W. Shi, C. Gao, G. Gao, B. Wang, Y. Wang, C. He and C. Niu, Gd-modified MnO_x for the selective catalytic reduction of NO by NH₃: the promoting effect of Gd on the catalytic performance and sulfur resistance, *Chem. Eng. J.*, 2018, **348**, 820–830.
- 58 Z. Ma, X. Wu, Y. Feng, Z. Si and D. Weng, Effects of WO₃ doping on stability and N₂O escape of MnO_x-CeO₂ mixed oxides as a low-temperature SCR catalyst, *Catal. Commun.*, 2015, **69**, 188–192.
- 59 M. Richter, A. Trunschke, U. Bentrup, K. W. Brzezinka, E. Schreier, M. Schneider, M. M. Pohl and R. Fricke, Selective Catalytic Reduction of Nitric Oxide by Ammonia over Egg-Shell MnO_x/NaY Composite Catalysts, *J. Catal.*, 2002, **206**, 98–113.
- 60 P. M. Sreekanth and P. G. Smirniotis, Selective Reduction of NO with CO Over Titania Supported Transition Metal Oxide Catalysts, *Catal. Lett.*, 2007, **122**, 37–42.
- 61 X. Tang, Y. Li, X. Huang, Y. Xu, H. Zhu, J. Wang and W. Shen, MnO_x-CeO₂ mixed oxide catalysts for complete oxidation of formaldehyde: effect of preparation method and calcination temperature, *Appl. Catal., B*, 2006, **62**, 265–273.
- 62 B. Thirupathi and P. G. Smirniotis, Effect of Nickel as Dopant in Mn/TiO₂ Catalysts for the Low-Temperature Selective Reduction of NO with NH₃, *Catal. Lett.*, 2011, **141**, 1399–1404.
- 63 J. Trawczyński, B. Bielak and W. Miśta, Oxidation of ethanol over supported manganese catalysts—effect of the carrier, *Appl. Catal., B*, 2005, **55**, 277–285.
- 64 V. Frizon, J.-M. Bassat, M. Pollet, E. Durand, J. Hernandez, K. Pajot, P. Vernoux and A. Demourgues, Tuning the Pr Valence State To Design High Oxygen Mobility, Redox and Transport Properties in the CeO₂-ZrO₂-PrO_x Phase Diagram, *J. Phys. Chem. C*, 2019, **123**, 6351–6362.

