


 Cite this: *RSC Adv.*, 2020, 10, 34916

# Magnetite nanoparticle decorated reduced graphene oxide for adsorptive removal of crystal violet and antifungal activities

 Mebrahtu Hagos Kahsay, <sup>\*a</sup> Neway Belachew, <sup>b</sup> Aschalew Tadesse <sup>c</sup> and K. Basavaiah <sup>d</sup>

This work reports the synthesis and application of magnetic rGO/Fe<sub>3</sub>O<sub>4</sub> NCs using a pod extract of *Dolichos lablab* L. as a reducing agent. GO was synthesized by a modified Hummers method, however GO was reduced using the plant extract to produce rGO. The as-synthesized rGO/Fe<sub>3</sub>O<sub>4</sub> NCs were characterized by UV-vis spectrophotometer, Fourier transform infrared (FT-IR) spectroscopy, FT-Raman spectroscopy, X-ray diffraction (XRD), field emission scanning electron microscopy supported with energy dispersed X-ray spectroscopy (FESEM-EDX), transmission electron microscopy (TEM) and vibrating sample magnetometer (VSM). The synthesis of magnetic rGO/Fe<sub>3</sub>O<sub>4</sub> NCs was confirmed from characterization results of FT-Raman, TEM and VSM. The FT-Raman results showed the D and G bands at 1306.92 cm<sup>-1</sup> and 1591 cm<sup>-1</sup> due to rGO and a peak at around 589 cm<sup>-1</sup> due to Fe<sub>3</sub>O<sub>4</sub> NPs that were anchored on rGO sheets; TEM results showed the synthesis of Fe<sub>3</sub>O<sub>4</sub> with an average particle size of 8.86 nm anchored on the surface of rGO sheets. The VSM result confirmed the superparamagnetic properties of the rGO/Fe<sub>3</sub>O<sub>4</sub> NCs with a saturation magnetization of 42 emu g<sup>-1</sup>. The adsorption capacity of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs towards crystal violet (CV) dye was calculated to be 62 mg g<sup>-1</sup>. The dye removal behavior fitted well with the Freundlich isotherm and the pseudo-second-order kinetic model implies possible chemisorption. Besides, rGO/Fe<sub>3</sub>O<sub>4</sub> NCs showed antifungal activities against *Trichophyton mentagrophytes* and *Candida albicans* by agar-well diffusion method with a zone inhibition of 24 mm and 21 mm, respectively. Therefore, rGO/Fe<sub>3</sub>O<sub>4</sub> NCs can be used as an excellent adsorbent to remove organic dye pollutants and kill pathogens.

 Received 17th August 2020  
 Accepted 9th September 2020

DOI: 10.1039/d0ra07061k

[rsc.li/rsc-advances](http://rsc.li/rsc-advances)

## 1. Introduction

Graphite oxide, also known as graphitic oxide or graphitic acid, is a compound of carbon, oxygen and hydrogen in variable ratios, obtained by treating graphite with strong oxidizers.<sup>1</sup> Most procedures have been reliant on strong oxidizing mixtures containing one or more concentrated acids and oxidizing materials during the synthesis of graphitic oxide.<sup>2,3</sup> The bulk material disperses in basic medium to yield monomolecular sheets or one atom thick in a closely packed honeycomb two dimensional (2D) lattice known as GO.<sup>4</sup> Hence, graphene is the single-layer form of graphite. The combination of GO or rGO with magnetite produces Fe<sub>3</sub>O<sub>4</sub>-graphene hybrid which has

a planar geometry, high conductivity, fascinating carrier transport properties, large surface area, strong magnetism, low cost and environmentally benign nature which has opened an opportunity for various applications.<sup>5-8</sup> Therefore, rGO/Fe<sub>3</sub>O<sub>4</sub> hybrids have reported for catalysis, water purification, sensors, toxic heavy metal removal, capacitors, bio-medical diagnosis therapy, microwave absorption, water desalination, photocatalysis and antimicrobial.<sup>7,9-15</sup> The hybrid combination of magnetic Fe<sub>3</sub>O<sub>4</sub> NPs and graphene sheets best produces rGO/Fe<sub>3</sub>O<sub>4</sub> NCs that have recognized properties such as great dispersibility, large surface area, superparamagnetism and fabulous extraction capacity.<sup>16</sup> The  $\pi$ - $\pi$  stacking, hydrogen bonding and electrostatic interaction between rGO/Fe<sub>3</sub>O<sub>4</sub> NCs and dye molecules are responsible for the adsorptive removal of dye molecules from aqueous solution.<sup>17</sup> Moreover, preceding reports indicated that rGO/Fe<sub>3</sub>O<sub>4</sub> NCs can efficiently remove toxic heavy metals,<sup>7,18</sup> fluoroquinolones,<sup>19</sup> organic dyes<sup>16,20</sup> and MB dye *via* degradation.<sup>17</sup>

In general, centrifugation and filtration methods are used to separate the adsorbent material from aqueous solution<sup>21</sup> even though these applications are time-consuming and require extra cost.<sup>22</sup> Compared with traditional centrifugation and

<sup>a</sup>Department of Chemistry, Woldia University, P.O. BOX 400, Woldia, Ethiopia. E-mail: hagosmebrahtu@gmail.com; mebrahtuh@wldu.edu.et

<sup>b</sup>Department of Chemistry, Debre Berhan University, P.O. BOX 445, Debre Berhan, Ethiopia

<sup>c</sup>Department of Applied Chemistry, Adama Science and Technology University, P.O. BOX 1888, Adama, Ethiopia

<sup>d</sup>Department of Inorganic and Analytical Chemistry, Andhra University, Visakhapatnam, 530003, India


filtration methods, magnetic separation method is an efficient, fast and economic method for the separation of magnetic adsorbents from the medium after the adsorption treatment of pollutants is completed.<sup>23</sup> Hence, it is important to synthesize magnetically separable and high surface area rGO/Fe<sub>3</sub>O<sub>4</sub> NCs for removal of water pollutants and treat pathogens. Diverse methods have been used to synthesize rGO/Fe<sub>3</sub>O<sub>4</sub> NCs, such as chemical co-precipitation,<sup>13,14</sup> solvothermal reduction,<sup>11,24</sup> chemical reduction,<sup>7</sup> and green synthesis.<sup>12,15,25</sup> Different types of adsorbents have been used as way of removal of organic compounds and metals from aqueous solution. For example, Harijan and Chandra<sup>26</sup> have stated facile fabrication of magnetite graphene composite through thermal reduction of graphene oxide to graphene in alkali medium with extreme sorption capacity for Cr<sup>6+</sup> (5.5 mg g<sup>-1</sup>) at pH = 6.6. The graphene sheets prohibited agglomeration of the Fe<sub>3</sub>O<sub>4</sub> NPs while enabling a good dispersion of the Fe<sub>3</sub>O<sub>4</sub> NPs and at the same time the specific surface area of the composite is considerably enhanced. Similarly, Sun *et al.*<sup>11</sup> have reported one step solvothermal synthetic route of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs for excellent removal of toxic dyes, *i.e.*, rhodamine B and malachite green with removal efficiency of 91% and 94%, respectively. He *et al.* have reported waste biofilms biosorbents to treat Cd<sup>2+</sup> from aqueous solutions. The maximum adsorption capacity of dry waste biofilms for Cd<sup>2+</sup> is 42 mg g<sup>-1</sup> when the initial concentration of Cd<sup>2+</sup> is 50 mg L<sup>-1</sup>.<sup>27</sup> Bionanomaterials such as *Saccharomyces cerevisiae* and nano Fe<sub>3</sub>O<sub>4</sub> encapsulated in a sodium alginate–polyvinyl alcohol matrix and *Penicillium* doped with nano Fe<sub>3</sub>O<sub>4</sub> entrapped in polyvinyl alcohol–sodium alginate gel beads have been reported to remove atrazine from aqueous solution by biodegradation.<sup>28,29</sup> Moreover, synthesis of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs through a facile and environmental benign approach is a prime concern for practical application. Plant extracts currently attract a tremendous research interest for synthesis of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs owing to environmentally friendly and ability to reduce GO into rGO. Gurunathan *et al.*<sup>30</sup> have recorded reduction of GO into rGO with spinach leaf extract as a simultaneous reducing and stabilizing agent. The plant extracts of *Solanum trilobatum*<sup>17</sup> and *Averrhoa carambola*<sup>12</sup> were previously reported as reducing agent for synthesis of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs. To the best of our information, *Dolichos lablab* L. has not been reported to synthesize rGO or rGO/Fe<sub>3</sub>O<sub>4</sub> NCs. *Dolichos lablab* L. is a plant that is extensively scattered in India that contains lectins sugar in the form of mannose/glucose specific,<sup>31</sup> galactose specific,<sup>32</sup> crude lipid, crude protein, insoluble dietary fibre, soluble dietary fibre, carbohydrate, and amino acids.<sup>33</sup> For this reason, the existence of many alternative phytoconstituents of the plant motivated the researchers to prepare rGO/Fe<sub>3</sub>O<sub>4</sub> NCs for different applications.

Herein, in this study, the researchers have synthesized rGO/Fe<sub>3</sub>O<sub>4</sub> NCs using a facile co-precipitation method of Fe<sub>3</sub>O<sub>4</sub> onto rGO sheet in the presence of extract of *Dolichos lablab* L. for the adsorptive removal of crystal violet (CV) and antifungal activity against pathogens. The pod extract of *Dolichos lablab* L. was used as reducing and capping agent during preparation of rGO and rGO/Fe<sub>3</sub>O<sub>4</sub> NCs. The crystal structure, electronic property and surface morphology of the as-synthesized materials were

investigated by UV-vis, FT-IR, FT-Raman, powder XRD, FESEM-EDX, TEM and VSM techniques. The CV dye was selected as a model water pollutant to investigate the adsorption capacity of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs. Besides, *Trichophyton mentagrophytes* and *Candida albicans* pathogens were chosen to examine the anti-fungal activities.

## 2. Experimental

### 2.1. Materials

All the chemicals in this paper were analytical grade acquired from Merck, HiMedia and Sigma-Aldrich and used without further purification. Iron(II) sulfate heptahydrate (FeSO<sub>4</sub>·7H<sub>2</sub>O), hydrogen peroxide (H<sub>2</sub>O<sub>2</sub>, 30% wt), sodium nitrate (NaNO<sub>3</sub>, 98%), concentrated sulfuric acid (H<sub>2</sub>SO<sub>4</sub>, 98% wt), potassium permanganate (KMnO<sub>4</sub>), crystal violet dye (C<sub>25</sub>H<sub>30</sub>ClN<sub>3</sub>) and sodium hydroxide (NaOH) were from Merck, India; iron(III) chloride hexahydrate (FeCl<sub>3</sub>·6H<sub>2</sub>O) from HiMedia, India; and Graphite flake with +100 mesh from Sigma-Aldrich, India. The standard strains of *Trichophyton mentagrophytes* and *Candida albicans* (fungus) were obtained from Adhya Biosciences Pvt. Ltd., Visakhapatnam. Milli-Q water was used in the experiment. Pocket-sized pH meter acquired from Hanna instruments was used to regulate the pH of the solutions. Hot Air Oven, Kemi was used to dry washed samples. *Dolichos lablab* L. pods were collected from market near Andhra University, Vishakhapatnam, India.

### 2.2. Preparation of aqueous pod extract of *Dolichos lablab* L

Pod layers were first detached from the seeds and cut into pieces by hand and shade dried in the laboratory for 21 days. Dried pods were grinded into powder using the Bajaj (Gx8) mixer grinder. The optimization of percent aqueous plant extract was taken based on our previous work.<sup>34</sup> To prepare 1% pod extract of *Dolichos lablab* L., 1 g pod powder was poured into 250 mL Erlenmeyer flask containing 100 mL Milli-Q water and heated at 70 °C for 20 min. The solution broth was permitted to cool and later filtered with Whatman no. 42 filter paper to create yellowish solution. Lastly, the plant extract suspension was preserved in a refrigerator at 4 °C for further utilize.

### 2.3. Synthesis of graphene oxide and reduced graphene oxide

GO was processed by modified Hummers strategy.<sup>1</sup> To prepare rGO from GO, pod extract of *Dolichos lablab* L. was used as a reducing agent. 100 mg of GO was added into round bottomed flask containing 50 mL Milli-Q water and sonicated for 30 min. Meanwhile 10 mL of 1% pod extract of *Dolichos lablab* L. was added and refluxed at 80 °C while stirring for 12 h to produce a black precipitate. Finally, rGO was collected by centrifugation at 12 000 rpm and dried at 100 °C in vacuum oven.

### 2.4. Synthesis of rGO-magnetite NCs using pod extract of *Dolichos lablab* L

The rGO/Fe<sub>3</sub>O<sub>4</sub> NCs were fabricated through co-precipitation using FeSO<sub>4</sub>·7H<sub>2</sub>O and FeCl<sub>3</sub>·6H<sub>2</sub>O in the presence of GO in



alkaline medium according to the procedure in ref. 35. One (1) mg mL<sup>-1</sup> dispersed GO was exfoliated into 100 mL of iron source solution containing both FeSO<sub>4</sub>·7H<sub>2</sub>O and FeCl<sub>3</sub>·6H<sub>2</sub>O salts (1 : 2 molar ratio) and it was sonicated for 1 h. Ten (10) mL of 1% pod extract of *Dolichos lablab* L. solution was added slowly to the above suspension of GO at 30 °C with vigorous stirring under nitrogen atmosphere for 1 h. In short period, 10 mL of ammonia solution was added drop wise to modify the mixture pH to a value of 10. Moreover, reducing agents in the plant extract may reduce Fe<sup>3+</sup> as well. Thereupon, the mixture was heated to 80 °C for 12 h to form dark colored solution indicating formation of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs. Finally, black colored rGO/Fe<sub>3</sub>O<sub>4</sub> NCs was produced, separated, washed with Milli-Q water and ethanol, and then dried in hot air oven at 60 °C for 12 h.

## 2.5. Characterization

The UV-visible absorption spectra were recorded using a (UNICAM UV 500, Thermo Electron Corporation) spectrophotometer in the range of 200–800 nm. FT-IR spectrum was recorded over the range of 4000–400 cm<sup>-1</sup> using a SHIMADZU-IR PRESTIGE-2 spectrometer. Raman spectrum was obtained using FT-Raman spectroscopy (Bruker RFS 27, USA) with laser source Nd (YAG 1064 nm) at 2 cm<sup>-1</sup> resolution. 16+ mW laser power was irradiated on rGO/Fe<sub>3</sub>O<sub>4</sub> NCs to collect Raman spectrum over the wide range 4000–50 cm<sup>-1</sup>. XRD patterns were recorded by PANalytical X'pert pro diffractometer at 0.02 degree per sec scan rate using Cu Kα<sub>1</sub> radiation (λ = 1.5406 Å, 45 kV, 40 mA). TEM images were acquired through (TEM model FEI TECNAI G2 S-Twin) at an accelerating voltage of 200 kV. The morphology of the sample was characterized using FE-SEM (FE-SEM, Zeiss Ultra-60) equipped with EDX. VSM was used to examine the magnetic property of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs (Lakeshore Cryotronics, Inc., Idea-VSM, model 7410, USA).

## 2.6. Batch mode adsorption studies

The adsorption experiments of CV dye on rGO/Fe<sub>3</sub>O<sub>4</sub> NCs took place with different initial concentrations of CV dye at different pH values at room temperature. 100 mL (5, 10, 15, 20 mg L<sup>-1</sup>) of CV dye solution was placed into 250 mL beaker and the pH (4–12) of the solution was maintained by using 0.1 M HCl/0.1 M NaOH solution. Afterward, 20 mg rGO/Fe<sub>3</sub>O<sub>4</sub> NCs was added to the beaker and kept agitated in an incubator for 220 min until equilibrium was established. The initial concentration of the dye was reported as C<sub>0</sub> and in the consecutive 20 min time interval, concentration of the dye was recorded as C<sub>t</sub>. The amount of CV dye adsorbed per gram of adsorbent at time, *t*, *q<sub>t</sub>* (mg g<sup>-1</sup>) and equilibrium, *q<sub>e</sub>* (mg g<sup>-1</sup>) were determined using (eqn (1) and (2)).

$$q_t = \frac{(C_0 - C_t)V}{m} \quad (1)$$

$$q_e = \frac{(C_0 - C_e)V}{m} \quad (2)$$

In addition, CV dye removal efficiency was calculated using (eqn (3)).

$$\eta(\%) = \frac{(C_0 - C_t)}{C_0} \times 100 \quad (3)$$

where, 'C<sub>0</sub>' is the initial CV dye concentration (mg L<sup>-1</sup>), 'C<sub>t</sub>' is concentration of CV dye at time, *t* (mg L<sup>-1</sup>), 'C<sub>e</sub>' is concentration of CV dye at equilibrium (mg L<sup>-1</sup>), 'V' is the volume of solution (L), 'm' is the mass of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs adsorbent (g) and 'η' is the dye removal percent (%). The adsorption isotherm was studied using Langmuir and Freundlich isotherm models, while, the kinetics was studied using pseudo-first and pseudo-second-order kinetic models.

## 2.7. Adsorption isotherms

To determine the maximum adsorption capacity of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs, the adsorption isotherm was analyzed by Langmuir<sup>36</sup> and Freundlich<sup>37</sup> isotherm models. The Langmuir adsorption isotherm argues consistent adsorbent surface activity and uni-layer adsorption, with partial adsorbent active sites, is revealed as in (eqn (4)).

$$\frac{C_e}{q_e} = \frac{1}{K_L q_{max}} + \frac{C_e}{q_{max}} \quad (4)$$

where, 'C<sub>e</sub>' is the equilibrium concentration of CV in the aqueous solution (mg L<sup>-1</sup>), 'K<sub>L</sub>' is the Langmuir adsorption constant (L mg<sup>-1</sup>) correlated to heat of adsorption, 'q<sub>max</sub>' is the maximal adsorption capacity of the adsorbent (mg g<sup>-1</sup>), and 'q<sub>e</sub>' is the amount of CV adsorbed per mass of adsorbent at equilibrium (mg g<sup>-1</sup>).

The Freundlich isotherm signifies surface heterogeneity of the adsorbent as well as multilayer coverage on the surface. The linear equation of Freundlich isotherm is expressed as in (eqn (5)).

$$\log q_e = \log K_F + \frac{1}{n} \log C_e \quad (5)$$

where, 'q<sub>e</sub>' is the quantity of dye adsorbed per unit weight of adsorbent (mg g<sup>-1</sup>), 'C<sub>e</sub>' is the equilibrium concentration of dye in the bulk solution (mg L<sup>-1</sup>), 'K<sub>F</sub>' is the Freundlich constant indicative of the relative adsorption capacity of the adsorbent (mg g<sup>-1</sup>) (L mg<sup>-1</sup>)<sup>1/n</sup> and 'n' is adsorption intensity in the Freundlich equation.

## 2.8. Adsorption kinetics

The physical and chemical properties of the adsorbent as well as mass transfer mechanisms are among the several prominent parameters to determine the adsorption mechanism. To revise the effect of adsorption time on CV dye removal by rGO/Fe<sub>3</sub>O<sub>4</sub> NCs, the mechanism of the adsorption process was studied by fitting pseudo-first-order and pseudo-second-order reactions to the experimental data. The adsorption equilibrium time of CV by rGO/Fe<sub>3</sub>O<sub>4</sub> NCs was 200 min. The Lagergren pseudo first-order kinetic model<sup>38</sup> is known as in (eqn (6)).

$$\ln(q_e - q_t) = \ln q_e - k_1 t \quad (6)$$



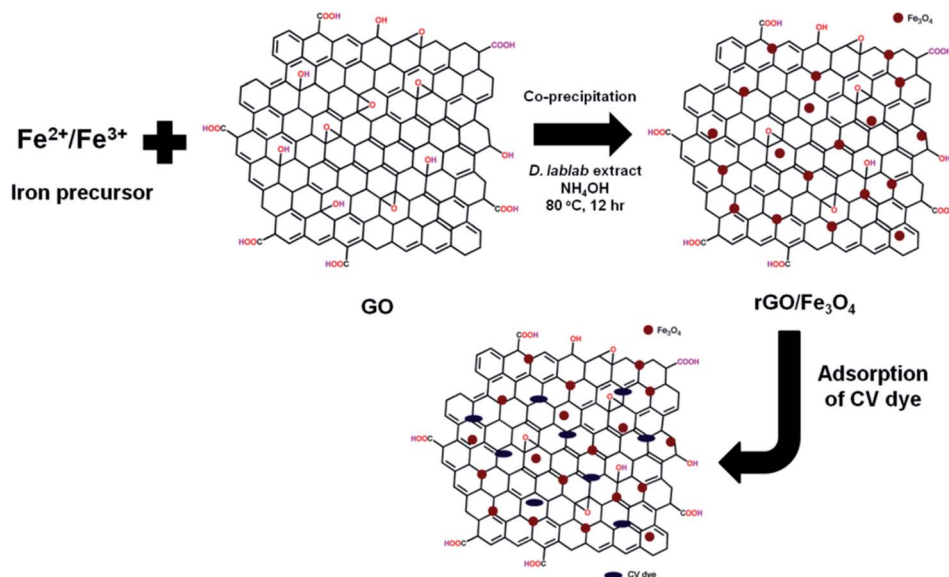


Fig. 1 Proposed mechanism of synthesis of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs using *Dolichos lablab* L. extract and removal of crystal violet dye by adsorption.

where, ' $q_e$ ' and ' $q_t$ ' are amount of CV dye adsorbed at equilibrium and time,  $t$  ( $\text{mg g}^{-1}$ ), ' $k_1$ ' is rate constant of pseudo-first-order kinetic model (min) and ' $t$ ' is time (min). Likewise, the pseudo-second-order kinetic model<sup>39</sup> is expressed as in (eqn (7)).

$$\frac{t}{q_t} = \frac{1}{k_2 q_e^2} + \frac{t}{q_e} \quad (7)$$

where, ' $k_2$ ' is the rate constant of pseudo-second-order ( $\text{g mg}^{-1} \text{min}^{-1}$ ), ' $q_t$ ' is the amount of CV dye adsorbed on surface of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs at time,  $t$  ( $\text{mg g}^{-1}$ ), ' $q_e$ ' is the equilibrium sorption capacity ( $\text{mg g}^{-1}$ ).

### 2.9. Antifungal activity against *Trichophyton mentagrophytes* and *Candida albicans*

The antifungal activity was carried out using agar-well diffusion method by employing 24 h cultures with given rGO/Fe<sub>3</sub>O<sub>4</sub>

NCs.<sup>40</sup> The medium was sterilized by autoclaving at 120 °C (15 lb per in<sup>2</sup>). About 20 mL of the nutrient agar medium/potato dextrose agar seeded with the respective fungal strains were transferred aseptically into each sterilized Petri plate. The plates were left at room temperature for solidification. Each plate, a single well of 6 mm diameter was made using a sterile borer. The rGO/Fe<sub>3</sub>O<sub>4</sub> NCs were freshly reconstituted with suitable solvent (DMSO) and tested at various concentrations (2.5  $\text{mg mL}^{-1}$ , 5  $\text{mg mL}^{-1}$ , 10  $\text{mg mL}^{-1}$ ). The samples (50  $\mu\text{L}$ ) and the control along with standard (clotrimazole (5  $\mu\text{g mL}^{-1}$ )) were placed in 6 mm diameter well. Then the fungal plates were incubated at  $28 \pm 2$  °C. Activity diameter of the zone of inhibition was measured using Himedia antibiotic zone scale.

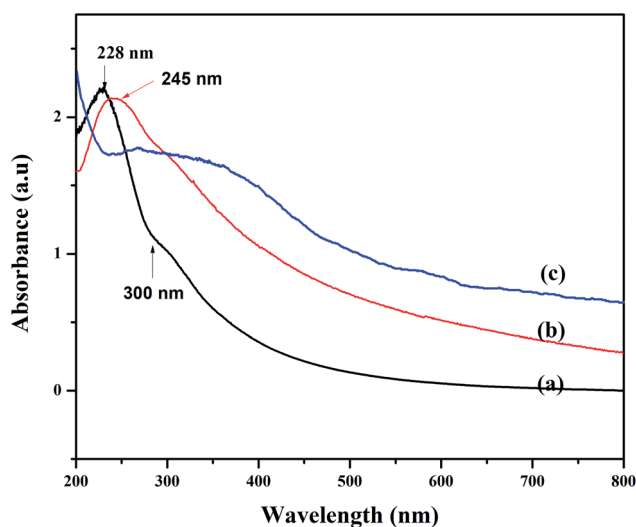


Fig. 2 UV-vis spectra of (a) GO, (b) rGO and (c) rGO/Fe<sub>3</sub>O<sub>4</sub> NCs.

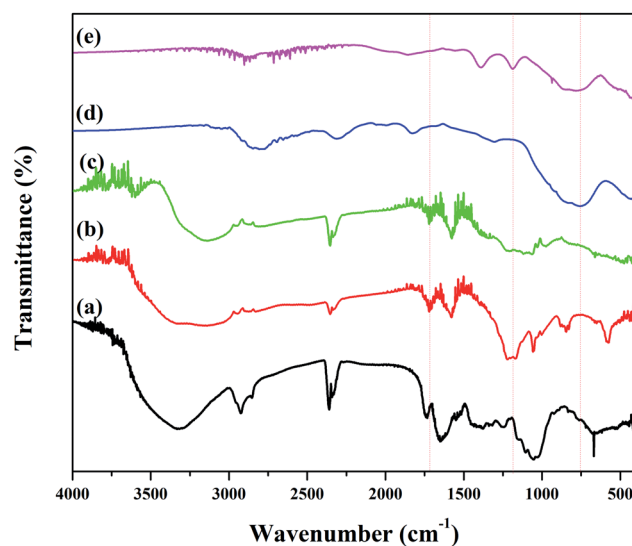


Fig. 3 FT-IR spectrum of (a) pod extract of *Dolichos lablab* L., (b) GO, (c) rGO, (d) Fe<sub>3</sub>O<sub>4</sub> NPs and (e) rGO/Fe<sub>3</sub>O<sub>4</sub> NCs.



### 3. Results and discussion

#### 3.1. Characterizations

**3.1.1. UV-vis analysis.** In this study, one pot co-precipitation green method was used to synthesize rGO/Fe<sub>3</sub>O<sub>4</sub> NCs using iron salts (Fe<sup>3+</sup>/Fe<sup>2+</sup>) in 2 : 1 molar ratio, GO and pod extract of *Dolichos lablab* L. A systematic schematic representation of synthesis of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs for the possible application of removal of CV dye is represented in Fig. 1. Fig. 2 depicts the absorption peak of the synthesized GO, rGO and rGO/Fe<sub>3</sub>O<sub>4</sub> NCs by using UV-vis spectrophotometer. The absorption peak of GO at 228 nm is due to  $\pi$  to  $\pi^*$  transition of the aromatic C=C bond,<sup>41</sup> Fig. 2(a). The reduction of GO using plant extract red shifted the peak to 245 nm is possible indication of synthesis of rGO, Fig. 2(b). Furthermore, a peak is observed for rGO/Fe<sub>3</sub>O<sub>4</sub> NCs at around 267 nm, Fig. 2(c).

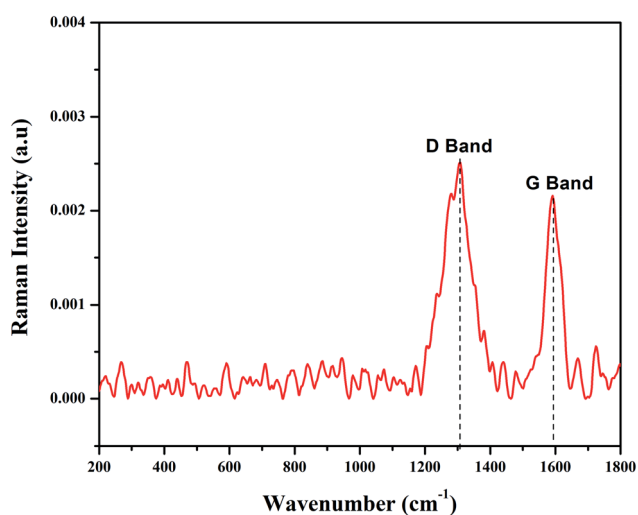


Fig. 4 FT-Raman spectrum of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs.

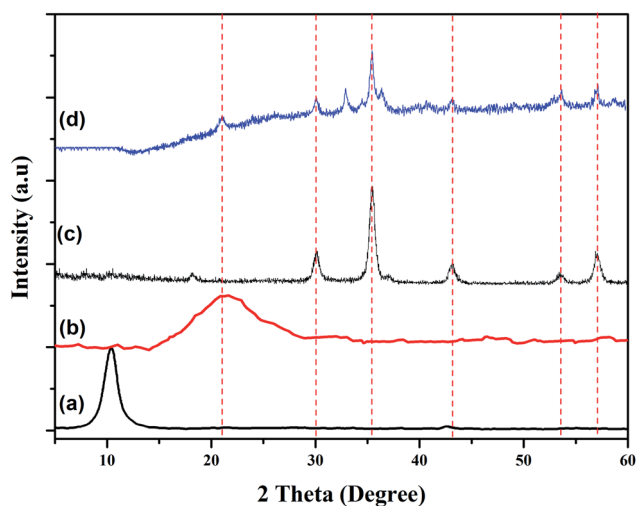


Fig. 5 Powder XRD patterns of (a) GO, (b) rGO, (c) Fe<sub>3</sub>O<sub>4</sub> NPs and (d) rGO/Fe<sub>3</sub>O<sub>4</sub> NCs.

**3.1.2. FT-IR analysis.** Fig. 3 depicts FT-IR spectrum to identify the functional groups of the plant extract, GO, rGO, Fe<sub>3</sub>O<sub>4</sub> NPs and rGO/Fe<sub>3</sub>O<sub>4</sub> NCs. Pod extract of *Dolichos lablab* L. showed absorption peaks at 3324, 2925, 1645, 1051 and 660 cm<sup>-1</sup> due to O-H stretching, sp<sup>3</sup> C-H stretching, C=O of amide or C=C stretching, C-O stretching and C-H bending, respectively (Fig. 3(a)). GO showed characteristic peaks at 3280 cm<sup>-1</sup>, 1702 cm<sup>-1</sup> and 1194 cm<sup>-1</sup> due to O-H, C=O and epoxy functional groups, respectively,<sup>42</sup> Fig. 3(b). The peak intensity 1194 cm<sup>-1</sup> is very much decreased in the rGO spectrum implies pod extract of *Dolichos lablab* L. is excellent reducing agent. The O-H stretching peaks in Fig. 3(a-c) were disappeared in the spectrum of both Fe<sub>3</sub>O<sub>4</sub> NPs and rGO/Fe<sub>3</sub>O<sub>4</sub> NCs are strong indications that the plant extract with carboxylic

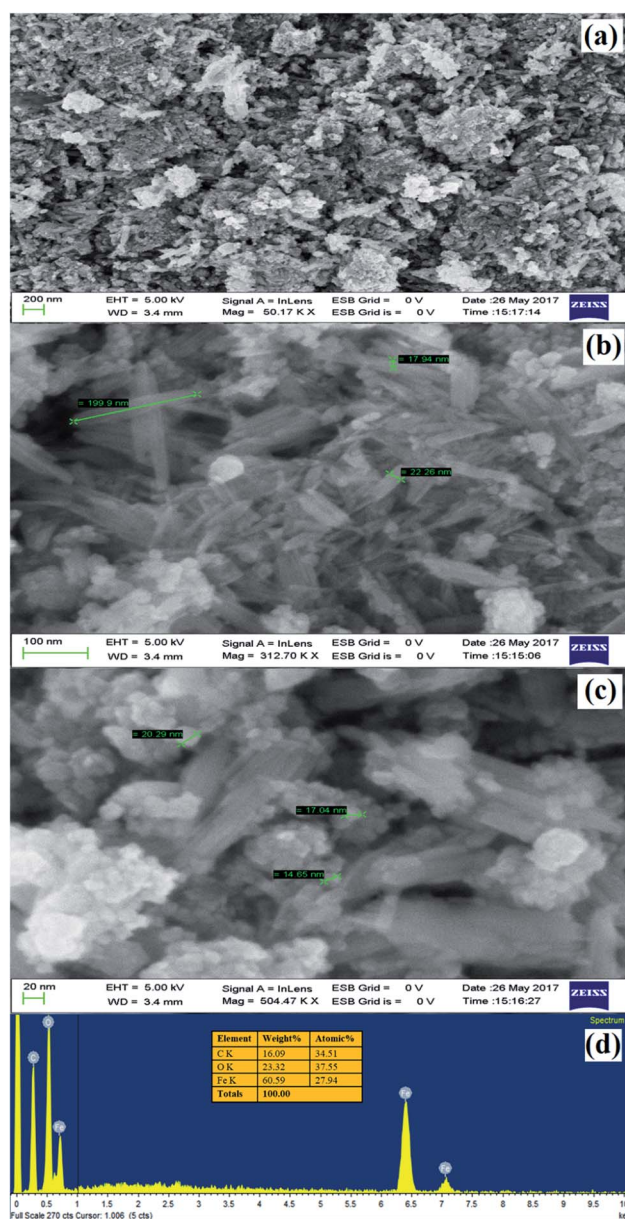


Fig. 6 (a) to (c) FE-SEM images of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs at different magnifications and (d) EDX spectrum of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs.



functional group was used as reducing agent. In addition, FT-IR spectrum of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs showed characteristic peaks at 1184 and 820 cm<sup>-1</sup> due to C–O stretching and CH<sub>2</sub> rocking, respectively. The two peaks at 509 and 403 cm<sup>-1</sup> were due to Fe–O stretching in rGO/Fe<sub>3</sub>O<sub>4</sub> NCs,<sup>43</sup> Fig. 3(d and e). The plant extract was used as reducing agent to facilitate reduction and formation of Fe<sub>3</sub>O<sub>4</sub> NPs on the surface of rGO sheets without the need to use hazardous reducing agent such as hydrazine.

**3.1.3. FT-Raman analysis.** FT-Raman spectroscopy is used to characterize carbon containing materials and to identify amorphous and crystalline carbon structures.<sup>44</sup> GO was allowed to react with Fe<sup>2+</sup>/Fe<sup>3+</sup> solutions in the presence of pod extract of *Dolichos lablab* L. as a reducing agent to produce rGO/Fe<sub>3</sub>O<sub>4</sub> NCs. The alkaloid, phenol, flavonoid, amino acid, protein, terpenoid and saponin are the already identified constituents of *Dolichos lablab* L. that are responsible for reducing GO to rGO.<sup>45</sup> The FT-Raman spectrum of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs is depicted in Fig. 4 and shows a clear formation of the nanocomposite. The FT-Raman shifts at 1306.92 cm<sup>-1</sup> (D band) and 1591 cm<sup>-1</sup> (G band) had ratio of  $I_D/I_G = 1.19$ . The D band is assigned to the breathing mode of the *k*-point phonons with A<sub>1g</sub> symmetry of

disordered graphite structure, whereas the G band introduces the E<sub>2g</sub> vibration mode between two sp<sup>2</sup> carbon atoms.<sup>46</sup> The three peaks at 269, 589, and 767 cm<sup>-1</sup> were related to Fe–O vibration of E<sub>g</sub> and A<sub>1g</sub> modes in Fe<sub>3</sub>O<sub>4</sub>. Hence, this result also proved magnetite nanoparticles were decorated on surfaces of rGO sheets.<sup>47</sup> Similarly, two peaks were absorbed at 1591 and 1307 cm<sup>-1</sup> for magnetite–rGO composites synthesized by using hydrazine hydrate as a reducing agent.<sup>7</sup> The G band of rGO (1601 cm<sup>-1</sup>, not shown here) is red shifted by 10 cm<sup>-1</sup> to 1591 cm<sup>-1</sup> in rGO/Fe<sub>3</sub>O<sub>4</sub> NCs.

**3.1.4. Powder XRD analysis.** The phase structures of GO, rGO, Fe<sub>3</sub>O<sub>4</sub> NPs and rGO/Fe<sub>3</sub>O<sub>4</sub> NCs were characterized through powder XRD as indicated in Fig. 5. The XRD pattern of GO showed strong and intense peak at  $2\theta = 10^\circ$  with a lattice reflection of (001), Fig. 5(a). The XRD analysis proved formation of rGO and displayed a broad and intense peak at  $2\theta = 21^\circ$  with a lattice reflection of (002) in Fig. 5(b). Similar broad peak was observed in the angle between 15°–30° during synthesis of rGO using heating coconut shell.<sup>48</sup> The XRD pattern of Fe<sub>3</sub>O<sub>4</sub> NPs and rGO/Fe<sub>3</sub>O<sub>4</sub> NCs in Fig. 5(c and d) displayed diffraction peak positions at  $2\theta$  values as 33.09°, 35.64°, 43.44°, 53.91°, 57.41°

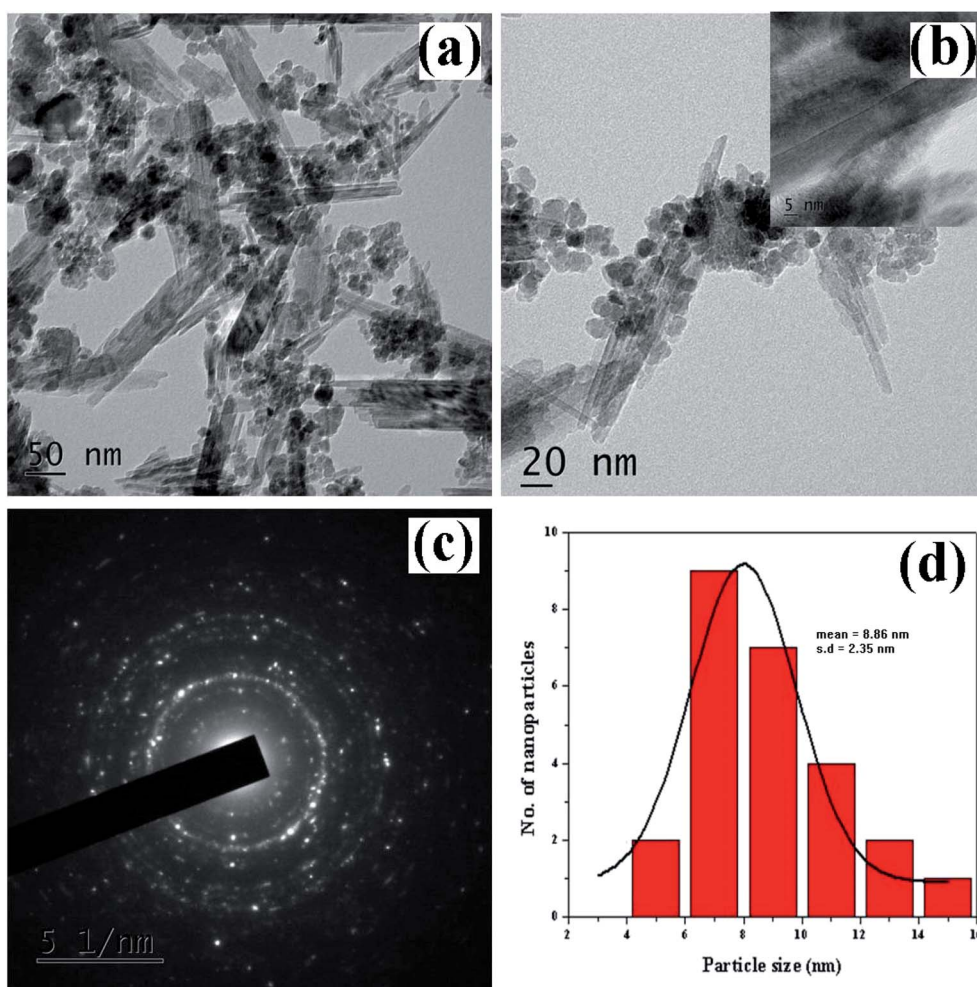


Fig. 7 TEM images of *Dolichos lablab* L. mediated rGO/Fe<sub>3</sub>O<sub>4</sub> NCs (a) 50 nm scale, (b) 20 nm scale, (c) SAED patterns of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs, and (d) size distribution histogram of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs.



and  $62.9^\circ$  with diffraction lines matching to (220), (311), (400), (422), (511) and (440), respectively, are consistent with the standard XRD data for the face centered cubic (fcc)  $\text{Fe}_3\text{O}_4$  structure (JCPDS card no. 19-0629). The peak at  $2\theta = 21^\circ$  (002) which is seen in the XRD pattern of rGO/ $\text{Fe}_3\text{O}_4$  NCs (Fig. 5(d)), confirmed  $\text{Fe}_3\text{O}_4$  NPs were anchored on the surfaces of rGO sheets.<sup>49</sup> The average crystallite size of the manufactured rGO/ $\text{Fe}_3\text{O}_4$  NCs was calculated to be 38 nm using the well-known Scherrer equation (eqn (8)).

$$D_{(hkl)} = \frac{k\lambda}{\beta \cos \theta} \quad (8)$$

where, ' $D_{(hkl)}$ ' is the average crystallite diameter (nm), ' $k$ ' is Scherrer constant (0.94), ' $\lambda$ ' is the X-ray wavelength, ' $\beta$ ' is the half width of XRD diffraction line, and ' $\theta$ ' is the Bragg's angle in degrees.

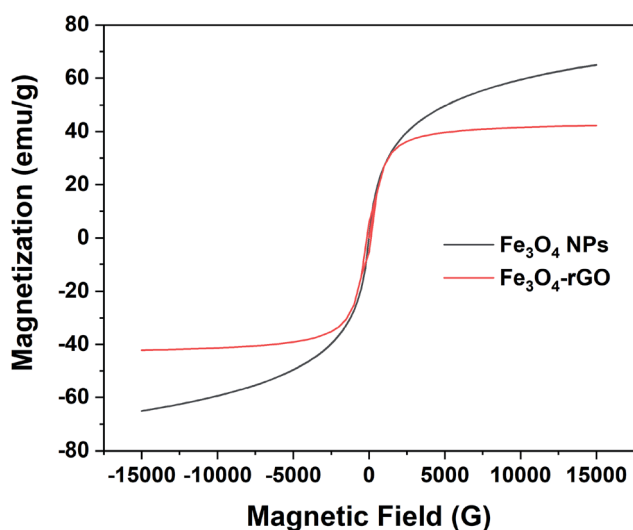


Fig. 8 Room temperature magnetization curve of pure magnetite and rGO/ $\text{Fe}_3\text{O}_4$  NCs.

**3.1.5. Morphology and structural analysis.** The morphological looks and surface characteristics of rGO/ $\text{Fe}_3\text{O}_4$  NCs were studied by using FESEM-EDX. Fig. 6(a-c) depicts FESEM images of  $\text{Fe}_3\text{O}_4$  NPs that were consistently distributed on the surface of rGO sheets. The size of the  $\text{Fe}_3\text{O}_4$  NPs from the image sources range from 9.75 to 14.85 nm. The EDX spectrum in Fig. 6(d) clearly identified the elemental existence of Fe, C and O with 27.94%, 34.51% and 37.55% by atomic mass, respectively. The TEM analysis was used to study the morphology and size of the synthesized rGO/ $\text{Fe}_3\text{O}_4$  NCs. Fig. 7(a and b) clearly shows spherical shaped  $\text{Fe}_3\text{O}_4$  NPs are homogeneously anchored at the surface of disorderly distributed rGO sheets. The SAED patterns of rGO/ $\text{Fe}_3\text{O}_4$  NCs in Fig. 7(c) showed both polycrystalline nature of  $\text{Fe}_3\text{O}_4$  and disorderly oriented nature of rGO sheets. The average particle size of  $\text{Fe}_3\text{O}_4$  in rGO/ $\text{Fe}_3\text{O}_4$  NCs was calculated to be 8.86 nm using (ImageJ) software, Fig. 7(d). There was small sign of aggregation of  $\text{Fe}_3\text{O}_4$  NPs observed on the surface of rGO sheets. Hence, the large surface area to volume ratio of the NCs causes the rGO/ $\text{Fe}_3\text{O}_4$  NCs to have an efficient adsorption property towards CV dye pollutant.

**3.1.6. VSM analysis.** The magnetic property of rGO/ $\text{Fe}_3\text{O}_4$  NCs was measured by VSM at room temperature and confirmed its superparamagnetic property. Fig. 8 shows the hysteresis loop of rGO/ $\text{Fe}_3\text{O}_4$  NCs with a magnetic saturation ( $M_s$ )  $42 \text{ emu g}^{-1}$  which was lower than that of L-Met capped  $\text{Fe}_3\text{O}_4$  NPs<sup>50</sup> indicated  $\text{Fe}_3\text{O}_4$  NPs were anchored on the surface of rGO sheets.

## 3.2. Adsorption study of CV dye

**3.2.1. Adsorption isotherms.** Fig. 9(a) shows UV-vis absorption spectra of CV dye adsorbed on rGO/ $\text{Fe}_3\text{O}_4$  NCs as a function of time, while Fig. 9(b) shows effect of pH on dye removal. The increase in the pH of dye solution (4, 7, 10, 12) resulted increase in the dye removal efficiency of the adsorbent by (34, 64, 90, 95%), respectively. The dye removal efficiency is lower at pH = 4 because the rGO/ $\text{Fe}_3\text{O}_4$  NCs surface is positively charged. Similarly, Duman *et al.*<sup>21</sup> have reported adsorption of CV dye onto magnetic OMWCNT- $\text{Fe}_3\text{O}_4$  NPs is lowest at pH = 2

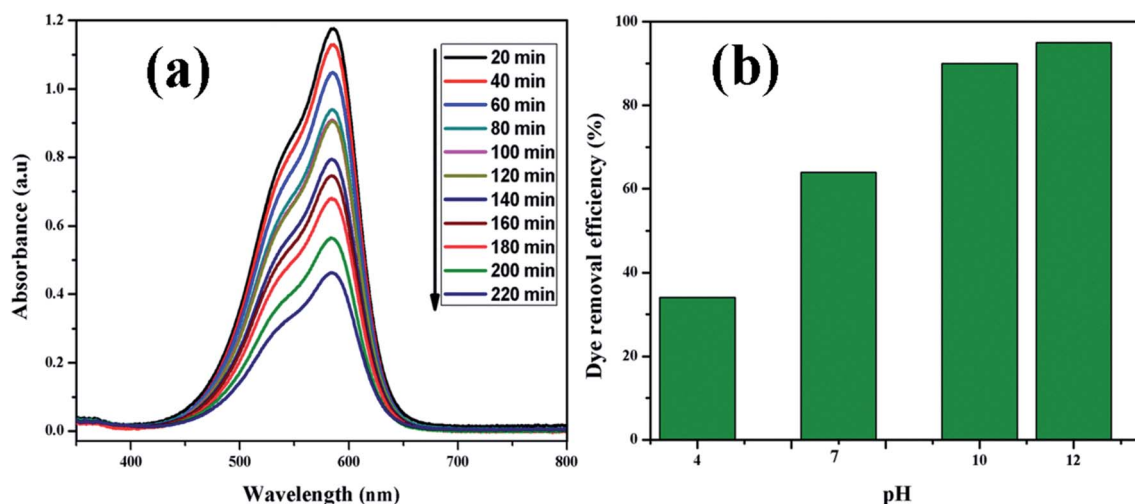


Fig. 9 (a) UV-vis absorption spectrum of CV ( $20 \text{ mg L}^{-1}$ ) adsorbed on rGO/ $\text{Fe}_3\text{O}_4$  NCs at different time and (b) effect of pH on dye removal.



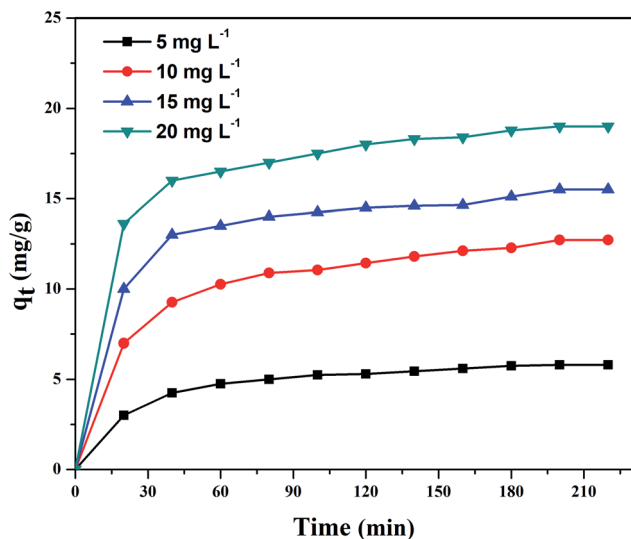


Fig. 10 Adsorption of CV dye on rGO/Fe<sub>3</sub>O<sub>4</sub> NCs at pH = 10 at different time.

(smaller than  $\text{pH}_{\text{PZC}}$ ). This is due to the electrostatic repulsion between positively charged adsorbent surfaces and positively charged CV dye. However, at the higher pH solution (pH = 12), the surface of the rGO/Fe<sub>3</sub>O<sub>4</sub> NCs became negatively charged which resulted to electrostatic forces of attraction between CV dye molecules and the adsorbent that increased adsorption efficiency to 95%. Fig. 10, depicts adsorption isotherm of CV dye

on rGO/Fe<sub>3</sub>O<sub>4</sub> NCs using different initial CV dye concentration at pH = 10. Dye adsorption increased with increasing initial concentration of organic dye pollutant. Fig. 11, describes Langmuir and Freundlich adsorption isotherm models of CV on the surface of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs. The correlation coefficients ( $r^2$ ) and other parameters from the models are presented in Table 1. The adsorption isotherm better fitted to Langmuir ( $r^2 = 0.998$ ) than Freundlich ( $r^2 = 0.992$ ). Hence, the adsorption mechanism was monolayer, *i.e.*, physical intermolecular attraction between the adsorbent and adsorbate predominated. Similar results were reported for the adsorption isotherms of various pollutant-adsorbent systems.<sup>51,52</sup> The monolayer adsorption maximum capacity ( $q_{\text{max}}$ ) of CV on rGO/Fe<sub>3</sub>O<sub>4</sub> NCs was found to be 62 mg g<sup>-1</sup>. Hence, current study shows rGO/Fe<sub>3</sub>O<sub>4</sub> NCs has better adsorption capacity than Fe<sub>3</sub>O<sub>4</sub> NPs alone towards CV dye<sup>53</sup> due to increased number of sites of functional groups in rGO/Fe<sub>3</sub>O<sub>4</sub> NCs.

**3.2.2. Adsorption kinetics.** The linear plots of pseudo-first-order and pseudo-second-order kinetic models for adsorption of CV dye on rGO/Fe<sub>3</sub>O<sub>4</sub> NCs are shown in Fig. 12. The kinetic model parameters and constants for the adsorption of CV dye on the surface of the adsorbent at room temperature are represented in Table 2. Adsorption of CV dye on surface of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs follows pseudo-second-order kinetics implies that the rate determining step is chemisorption.<sup>54</sup> Similar results were reported for the adsorption kinetics of various pollutants onto activated carbon cloth.<sup>55-57</sup> Therefore, adsorption was facilitated due to the interaction of cationic dye (CV) and rGO

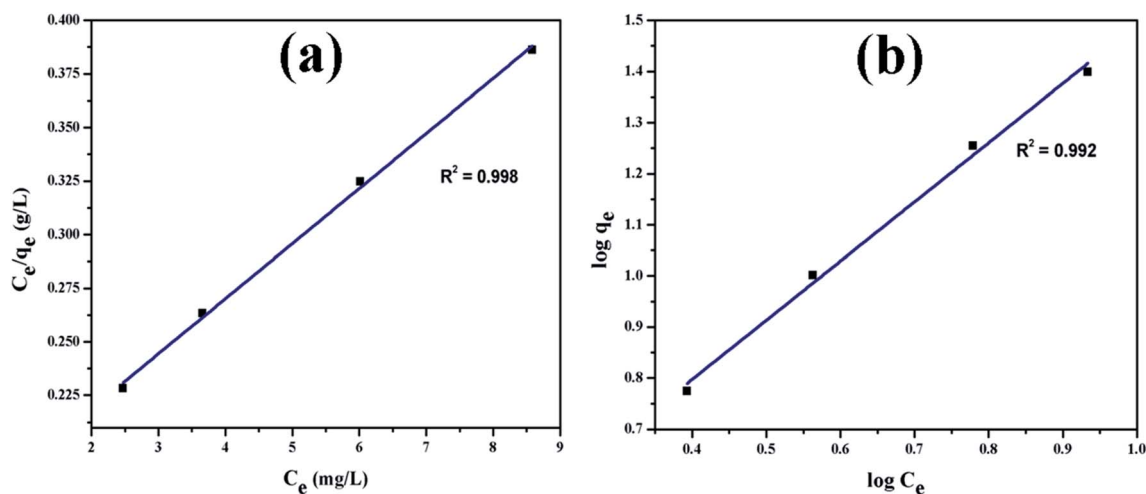


Fig. 11 Adsorption isotherm plots of CV dye (a) Langmuir and (b) Freundlich isotherm.

Table 1 Adsorption parameters of Langmuir and Freundlich equations and correlation coefficients for the adsorption of CV dye onto rGO/Fe<sub>3</sub>O<sub>4</sub> NCs adsorbent at 25 °C

Adsorbent	Langmuir parameters			Freundlich parameters		
	$q_{\text{max}}$ (mg g <sup>-1</sup> )	$K_L$ (L mg <sup>-1</sup> )	$r^2$	$K_F$ (mg g <sup>-1</sup> ) (L mg <sup>-1</sup> ) <sup>1/n</sup>	$n$	$r^2$
rGO/Fe <sub>3</sub> O <sub>4</sub> NCs	62	0.150	0.9985	2.14	0.870	0.9925



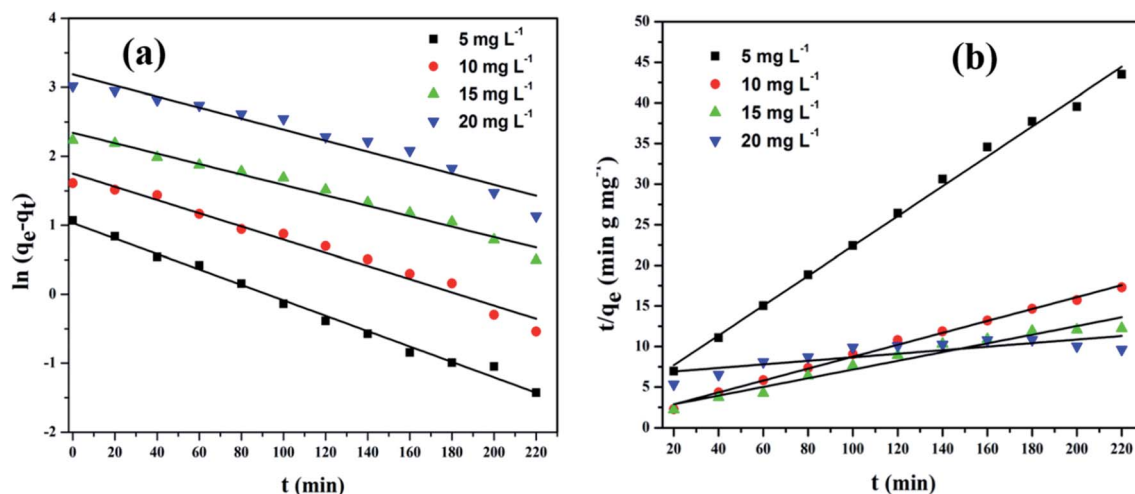


Fig. 12 (a) Pseudo-first-order and (b) pseudo-second-order kinetic plots of CV on rGO/Fe<sub>3</sub>O<sub>4</sub> NCs.

Table 2 Kinetic parameters and correlation coefficients for the adsorption of CV dye onto rGO/Fe<sub>3</sub>O<sub>4</sub> NCs at 25 °C

Initial CV concentration (mg L <sup>-1</sup> )	Pseudo-first-order				Pseudo-second-order			
	$q_{e, \text{exp}}$ (mg g <sup>-1</sup> )	$k_1$ (min <sup>-1</sup> )	$q_{t, \text{cal}}$ (mg g <sup>-1</sup> )	$r^2$	$k_2$ (g mg <sup>-1</sup> min <sup>-1</sup> )	$q_{t, \text{cal}}$ (mg g <sup>-1</sup> )	$h$ (mg g <sup>-1</sup> min <sup>-1</sup> )	$r^2$
5	12.64	$1.1 \times 10^{-2}$	1.348	0.9923	$8.4 \times 10^{-3}$	12.12	1.342	0.9968
10	33.64	$9.0 \times 10^{-3}$	1.598	0.9737	$3.9 \times 10^{-3}$	32.52	4.413	0.9957
15	44.93	$7.0 \times 10^{-3}$	1.827	0.9745	$1.6 \times 10^{-3}$	42.26	3.230	0.9982
20	62.00	$7.0 \times 10^{-3}$	1.962	0.9346	$7.3 \times 10^{-5}$	61.97	0.2806	0.9989

sheets through the oxygen functional groups and vacancy defects, by either electrostatic or  $\pi$ - $\pi$  interactions.<sup>58</sup> The maximum adsorption capacity of Fe<sub>3</sub>O<sub>4</sub>-rGO NCs synthesized by solvothermal method against methyl violet dye has been reported 196 mg g<sup>-1</sup> by Cherukutty *et al.*<sup>59</sup> Similarly, the maximum adsorption capacity of Fe<sub>3</sub>O<sub>4</sub>/GO hybrid to remove methylene blue dye from aqueous solution at 35 °C has been reported 96.05 mg g<sup>-1</sup> by Liao *et al.*<sup>60</sup> In addition, successful photocatalytic degradation of malachite green using Ag<sub>3</sub>-PO<sub>4</sub>@MWCNTs@Cr : SrTiO<sub>3</sub> composite from aqueous solution under sunlight or visible light irradiation has also been reported by Lin *et al.*<sup>61</sup>

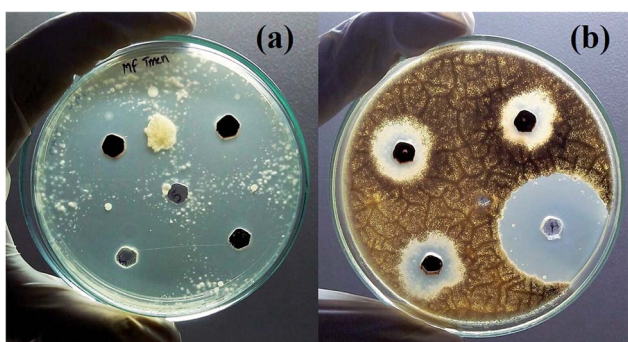


Fig. 13 Antifungal activities of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs against (a) *Trichophyton mentagrophytes* and (b) *Candida albicans*.

### 3.3. Antifungal activity of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs

Finally, the product rGO/Fe<sub>3</sub>O<sub>4</sub> NCs showed antifungal activity against *Trichophyton mentagrophytes* and *Candida albicans* with maximum zone of inhibition of 24 mm and 21 mm, respectively. See both Fig. 13 and 14. Mohanta *et al.*<sup>62</sup> reported bio-synthesized AgNPs using aqueous leaf extract of *Erythrina suberosa* (Roxb.) showed antifungal activity against *Trichophyton*

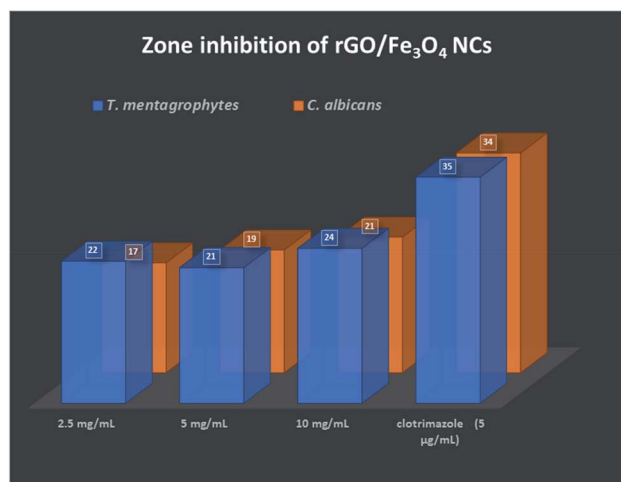


Fig. 14 Zone inhibition of rGO/Fe<sub>3</sub>O<sub>4</sub> NCs against pathogens.



*mentagrophytes* with inhibition zone of  $16 \pm 0.8$  mm, but no zone of inhibition was observed against *Candida albicans*. In addition, green synthesized ZnS NPs using *Phyllanthus niruri* plant extract and thorn-like ZnO NPs synthesized by sol-gel method both showed antifungal activity against *Candida albicans* with maximum inhibition zone of 32 mm and  $20 \pm 1.5$  mm, respectively.<sup>63,64</sup> Hence, the as-synthesized rGO/Fe<sub>3</sub>O<sub>4</sub> NCs have showed better antifungal activity against the above studied fungus and therefore can be used as antimicrobial applications.

## 4. Conclusions

Eco-friendly, cost-effective and single-step green co-precipitation synthesis of magnetically separable rGO/Fe<sub>3</sub>O<sub>4</sub> NCs using pod extract of *Dolichos lablab* L. as reducing agent was reported. The result of TEM analysis showed the average particle size of Fe<sub>3</sub>O<sub>4</sub> NPs in the as-synthesized rGO/Fe<sub>3</sub>O<sub>4</sub> NCs was 8.86 nm. The maximum CV dye removal efficiency of the adsorbent was calculated to be 95% at pH = 12. The adsorption mechanism well fitted to Langmuir than Freundlich isotherm and followed pseudo-second-order kinetics. *Dolichos lablab* L. mediated rGO/Fe<sub>3</sub>O<sub>4</sub> NCs can be used as efficient removal of toxic dyes and metals from contaminated water and antifungal against microorganism pathogens.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

Authors acknowledge UGC-SAP-DRS-I (No. F.540/18/DRS-I/2016) and DST-FIST (5R/FIST/CSI-241/2012(C)), Department of Inorganic and Analytical Chemistry, Andhra University. Mebrahtu Hagos Kahsay, Aschalew Tadesse and Neway Belachew would like to acknowledge Ministry of Science and Higher Education, Federal Democratic Republic of Ethiopia for financial support.

## References

- W. S. Hummers and R. E. Offeman, Preparation of graphitic oxide, *J. Am. Chem. Soc.*, 1958, **80**, 1339.
- U. Hofmann and A. Frenzel, Quellung von Graphit und die Bildung von Graphitsäure, *Ber. Dtsch. Chem. Ges. A*, 1930, **63**, 1248–1262.
- L. Staudenmaier, Verfahren zur Darstellung der Graphitsäure, *Ber. Dtsch. Chem. Ges.*, 1898, **31**, 1481–1487.
- A. Tiwari and M. Syväjärvi, *Graphene Materials: Fundamentals and Emerging Applications*, 2015.
- Z. Geng, Y. Lin, X. Yu, Q. Shen, L. Ma, Z. Li, *et al.*, Highly efficient dye adsorption and removal: a functional hybrid of reduced graphene oxide-Fe<sub>3</sub>O<sub>4</sub> nanoparticles as an easily regenerative adsorbent, *J. Mater. Chem.*, 2012, **22**, 3527.
- A. Meidanchi and O. Akhavan, Superparamagnetic zinc ferrite spinel-graphene nanostructures for fast wastewater purification, *Carbon*, 2014, **69**, 230–238.
- V. Chandra, J. Park, Y. Chun, J. W. Lee, I.-C. Hwang and K. S. Kim, Water-Dispersible Magnetite-Reduced Graphene Oxide Composites for Arsenic Removal, *ACS Nano*, 2010, **4**, 3979–3986.
- Z. P. Niu, F. X. Li, B. G. Wang, L. Sheng and D. Y. Xing, Spin transport in magnetic graphene superlattices, *Eur. Phys. J. B*, 2008, **66**, 245–250.
- G. Wang, B. Wang, J. Park, J. Yang, X. Shen and J. Yao, Synthesis of enhanced hydrophilic and hydrophobic graphene oxide nanosheets by a solvothermal method, *Carbon*, 2009, **47**, 68–72.
- J. Shen, Y. Hu, M. Shi, N. Li, H. Ma and M. Ye, One Step Synthesis of Graphene Oxide-Magnetic Nanoparticle Composite, *J. Phys. Chem. C*, 2010, **114**, 1498–1503.
- H. Sun, L. Cao and L. Lu, Magnetite/reduced graphene oxide nanocomposites: One step solvothermal synthesis and use as a novel platform for removal of dye pollutants, *Nano Res.*, 2011, **4**, 550–562.
- D. K. Padhi, T. K. Panigrahi, K. Parida, S. K. Singh and P. M. Mishra, Green Synthesis of Fe<sub>3</sub>O<sub>4</sub>/RGO Nanocomposite with Enhanced Photocatalytic Performance for Cr(VI) Reduction, Phenol Degradation, and Antibacterial Activity, *ACS Sustainable Chem. Eng.*, 2017, **5**, 10551–10562.
- M. Zong, Y. Huang, Y. Zhao, L. Wang, P. Liu, Y. Wang, *et al.*, One-pot simplified co-precipitation synthesis of reduced graphene oxide/Fe<sub>3</sub>O<sub>4</sub> composite and its microwave electromagnetic properties, *Mater. Lett.*, 2013, **106**, 22–25.
- T. N. Narayanan, Z. Liu, P. R. Lakshmy, W. Gao, Y. Nagaoka, D. Sakthi Kumar, *et al.*, Synthesis of reduced graphene oxide-Fe<sub>3</sub>O<sub>4</sub> multifunctional freestanding membranes and their temperature dependent electronic transport properties, *Carbon*, 2012, **50**, 1338–1345.
- T. Peik-See, A. Pandikumar, L. H. Ngee, H. N. Ming and C. C. Hua, Magnetically separable reduced graphene oxide/iron oxide nanocomposite materials for environmental remediation, *Catal. Sci. Technol.*, 2014, **4**, 4396–4405.
- T. Qi, C. Huang, S. Yan, X.-J. Li and S.-Y. Pan, Synthesis, characterization and adsorption properties of magnetite/reduced graphene oxide nanocomposites, *Talanta*, 2015, **144**, 1116–1124.
- M. Vinothkannan, C. Karthikeyan, G. Gnana kumar, A. R. Kim and D. J. Yoo, One-pot green synthesis of reduced graphene oxide (RGO)/Fe<sub>3</sub>O<sub>4</sub> nanocomposites and its catalytic activity toward methylene blue dye degradation, *Spectrochim. Acta, Part A*, 2015, **136**, 256–264.
- N. T. V. Hoan, N. T. A. Thu, H. Van Duc, N. D. Cuong, D. Q. Khieu and V. Vo, Fe<sub>3</sub>O<sub>4</sub>/Reduced Graphene Oxide Nanocomposite: Synthesis and Its Application for Toxic Metal Ion Removal, *Journal of Chemistry*, 2016, **2016**, 1–10.
- Y. Tang, H. Guo, L. Xiao, S. Yu, N. Gao and Y. Wang, Synthesis of reduced graphene oxide/magnetite composites and investigation of their adsorption performance of fluoroquinolone antibiotics, *Colloids Surf., A*, 2013, **424**, 74–80.



- 20 Y.-W. Liu, M.-X. Guan, L. Feng, S.-L. Deng, J.-F. Bao, S.-Y. Xie, *et al.*, Facile and straightforward synthesis of superparamagnetic reduced graphene oxide-Fe<sub>3</sub>O<sub>4</sub> hybrid composite by a solvothermal reaction, *Nanotechnology*, 2013, **24**, 025604.
- 21 O. Duman, S. Tunç, B. K. Bozoğlan and T. G. Polat, Removal of triphenylmethane and reactive azo dyes from aqueous solution by magnetic carbon nanotube-κ-carrageenan-Fe<sub>3</sub>O<sub>4</sub> nanocomposite, *J. Alloys Compd.*, 2016, **687**, 370–383.
- 22 O. Duman, C. Özcan, T. G. Polat and S. Tunç, Carbon nanotube-based magnetic and non-magnetic adsorbents for the high-efficiency removal of diquat dibromide herbicide from water: OMWCNT, OMWCNT-Fe<sub>3</sub>O<sub>4</sub> and OMWCNT-κ-carrageenan-Fe<sub>3</sub>O<sub>4</sub> nanocomposites, *Environ. Pollut.*, 2019, **244**, 723–732.
- 23 O. Duman, S. Tunç, T. G. Polat and B. K. Bozoğlan, Synthesis of magnetic oxidized multiwalled carbon nanotube-κ-carrageenan-Fe<sub>3</sub>O<sub>4</sub> nanocomposite adsorbent and its application in cationic Methylene Blue dye adsorption, *Carbohydr. Polym.*, 2016, **147**, 79–88.
- 24 S. Dubin, S. Gilje, K. Wang, V. C. Tung, K. Cha, A. S. Hall, *et al.*, A one-step, solvothermal reduction method for producing reduced graphene oxide dispersions in organic solvents, *ACS Nano*, 2010, **4**, 3845–3852.
- 25 R. Krishna, C. Dias, J. Ventura and E. Titus, Green and facile decoration of Fe<sub>3</sub>O<sub>4</sub> nanoparticles on reduced graphene oxide, *Mater. Today: Proc.*, 2016, **3**, 2807–2813.
- 26 D. K. L. Harijan and V. Chandra, Environment friendly synthesis of magnetite-graphene composite for adsorption of toxic chromium(vi) ions from drinking water, *Environ. Prog. Sustainable Energy*, 2016, **35**, 700–705.
- 27 H. J. He, Z. H. Xiang, X. J. Chen, H. Chen, H. Huang, M. Wen and C. P. Yang, Biosorption of Cd(II) from synthetic wastewater using dry biofilms from biotrickling filters, *Int. J. Environ. Sci. Technol.*, 2018, **15**(7), 1491–1500.
- 28 X. Wu, H. He, W. L. Yang, J. Yu and C. Yang, Efficient removal of atrazine from aqueous solutions using magnetic *Saccharomyces cerevisiae* bionanomaterial, *Appl. Microbiol. Biotechnol.*, 2018, **102**(17), 7597–7610.
- 29 J. Yu, H. He, W. L. Yang, C. Yang, G. Zeng and X. Wu, Magnetic bionanoparticles of *Penicillium* sp. yz11-22N2 doped with Fe<sub>3</sub>O<sub>4</sub> and encapsulated within PVA-SA gel beads for atrazine removal, *Bioresour. Technol.*, 2018, **260**, 196–203.
- 30 S. Gurunathan, J. W. Han, V. Eppakayala, A. A. Dayem, D.-N. Kwon and J.-H. Kim, Biocompatibility effects of biologically synthesized graphene in primary mouse embryonic fibroblast cells, *Nanoscale Res. Lett.*, 2013, **8**, 393.
- 31 N. S. Kumar, N. Siva Kumar and D. Rajagopal Rao, The nature of lectins from Dolichos lablab, *J. Biosci.*, 1986, **10**, 95–109.
- 32 V. L. Latha, R. N. Rao and S. K. Nadimpalli, Affinity purification, physicochemical and immunological characterization of a galactose-specific lectin from the seeds of Dolichos lablab (Indian lablab beans), *Protein Expression Purif.*, 2006, **45**, 296–306.
- 33 C.-F. Chau, P. C.-K. Cheung and Y.-S. Wong, Chemical composition of three underutilized legume seeds grown in China, *Food Chem.*, 1998, **61**, 505–509.
- 34 M. H. Kahsay, D. RamaDevi, Y. Pavan Kumar, B. Sathish Mohan, A. Tadesse, G. Battu, *et al.*, Synthesis of silver nanoparticles using aqueous extract of dolichos lablab for reduction of 4-nitrophenol, antimicrobial and anticancer activities, *OpenNano*, 2018, **3**, 28–37.
- 35 X. Luo, C. Wang, S. Luo, R. Dong, X. Tu and G. Zeng, Adsorption of As(III) and As(V) from water using magnetite Fe<sub>3</sub>O<sub>4</sub>-reduced graphite oxide-MnO<sub>2</sub> nanocomposites, *Chem. Eng. J.*, 2012, **187**, 45–52.
- 36 I. Langmuir, The adsorption of gases on plane surfaces of glass, mica and platinum, *J. Am. Chem. Soc.*, 1918, **40**, 1361–1403.
- 37 H. Freundlich, Kapillarchemie und Physiologie, *Zeitschrift für Chemie und Industrie der Kolloide*, 1907, **2**, 97–102.
- 38 S. Y. Lagergren, *Zur Theorie der sogenannten Adsorption gelöster Stoffe*, 1898.
- 39 D. Robati, Pseudo-second-order kinetic equations for modeling adsorption systems for removal of lead ions using multi-walled carbon nanotube, *J. Nanostruct. Chem.*, 2013, **3**, 55.
- 40 M. A. Pfaller, V. Chaturvedi, A. Espinel-Ingroff, M. A. Ghannoum, L. L. Gosey, F. C. Odds and J. H. Rex, *et al.*, Reference method for broth dilution antifungal susceptibility testing of yeasts; approved standard, *National Committee for Clinical Laboratory Standards document M27-A 22*, 2002, pp. 1–30.
- 41 K. Krishnamoorthy, G.-S. Kim and S. J. Kim, Graphene nanosheets: Ultrasound assisted synthesis and characterization, *Ultrason. Sonochem.*, 2013, **20**, 644–649.
- 42 D. R. Dreyer, S. Park, C. W. Bielawski and R. S. Ruoff, The chemistry of graphene oxide, *Chem. Soc. Rev.*, 2010, **39**, 228–240.
- 43 R. D. Waldron, Infrared Spectra of Ferrites, *Phys. Rev.*, 1955, **99**, 1727–1735.
- 44 A. C. Ferrari, J. C. Meyer, V. Scardaci, C. Casiraghi, M. Lazzeri, F. Mauri, *et al.*, Raman Spectrum of Graphene and Graphene Layers, *Phys. Rev. Lett.*, 2006, **97**, 187401–187404.
- 45 M. H. Kahsay, A. Tadesse, D. RamaDevi, N. Belachew and K. Basavaiah, Green synthesis of zinc oxide nanostructures and investigation of their photocatalytic and bactericidal applications, *RSC Adv.*, 2019, **9**, 36967–36981.
- 46 S. Stankovich, D. A. Dikin, R. D. Piner, K. A. Kohlhaas, A. Kleinhammes, Y. Jia, *et al.*, Synthesis of graphene-based nanosheets via chemical reduction of exfoliated graphite oxide, *Carbon*, 2007, **45**, 1558–1565.
- 47 L. Li, P. Gao, S. Gai, F. He, Y. Chen, M. Zhang, *et al.*, Ultra small and highly dispersed Fe<sub>3</sub>O<sub>4</sub> nanoparticles anchored on reduced graphene for supercapacitor application, *Electrochim. Acta*, 2016, **190**, 566–573.
- 48 A. Y. Nugraheni, M. Nasrullah, F. A. Prasetya and F. Astuti, Study on Phase, Molecular Bonding, and Bandgap of Reduced Graphene Oxide Prepared by Heating Coconut Shell, *Mater. Sci. Forum*, 2015, **827**, 285–289.



- 49 H.-P. Cong, J.-J. He, Y. Lu and S.-H. Yu, Water-Soluble Magnetic-Functionalized Reduced Graphene Oxide Sheets: In situ Synthesis and Magnetic Resonance Imaging Applications, *Small*, 2010, **6**, 169–173.
- 50 N. Belachew, D. R. Devi and K. Basavaiah, Facile green synthesis of L-methionine capped magnetite nanoparticles for adsorption of pollutant Rhodamine B, *J. Mol. Liq.*, 2016, **224**, 713–720.
- 51 O. Duman, S. Tunç and T. G. Polat, Determination of adsorptive properties of expanded vermiculite for the removal of C. I. Basic Red 9 from aqueous solution: Kinetic, isotherm and thermodynamic studies, *Appl. Clay Sci.*, 2015, **109–110**, 22–32.
- 52 O. Duman, S. Tunç and T. Gürkan Polat, Adsorptive removal of triarylmethane dye (Basic Red 9) from aqueous solution by sepiolite as effective and low-cost adsorbent, *Microporous Mesoporous Mater.*, 2015, **210**, 176–184.
- 53 K. Basavaiah, M. H. Kahsay and D. RamaDevi, Green synthesis of magnetite nanoparticles using aqueous pod extract of *Dolichos lablab* L for an efficient adsorption of crystal violet, *Emergent Mater.*, 2018, **1**, 121–132.
- 54 Y. S. Ho and G. McKay, Pseudo-second order model for sorption processes, *Process Biochem.*, 1999, **34**, 451–465.
- 55 O. Duman and E. Ayranci, Attachment of benzo-crown ethers onto activated carbon cloth to enhance the removal of chromium, cobalt and nickel ions from aqueous solutions by adsorption, *J. Hazard. Mater.*, 2010, **176**, 231–238.
- 56 O. Duman and E. Ayranci, Adsorptive removal of cationic surfactants from aqueous solutions onto high-area activated carbon cloth monitored by in situ UV spectroscopy, *J. Hazard. Mater.*, 2010, **174**, 359–367.
- 57 E. Ayranci and O. Duman, *In Situ* UV-Visible Spectroscopic Study on the Adsorption of some Dyes onto Activated Carbon Cloth, *Sep. Sci. Technol.*, 2009, **44**, 3735–3752.
- 58 C. R. Minitha, M. Lalitha, Y. L. Jeyachandran, L. Senthilkumar and R. T. Rajendra Kumar, Adsorption behaviour of reduced graphene oxide towards cationic and anionic dyes: Co-action of electrostatic and  $\pi$ - $\pi$  interactions, *Mater. Chem. Phys.*, 2017, **194**, 243–252.
- 59 C. R. Minitha, M. Martina Susan Arachy and R. T. Rajendra Kumar, Influence of Fe<sub>3</sub>O<sub>4</sub> nanoparticles decoration on dye adsorption and magnetic separation properties of Fe<sub>3</sub>O<sub>4</sub>/rGO nanocomposites, *Sep. Sci. Technol.*, 2018, **53**, 2159–2169.
- 60 N. Liao, Z. Liu, W. Zhang, S. Gong, D. Ren, L. Ke, *et al.*, Preparation of a novel Fe<sub>3</sub>O<sub>4</sub>/graphene oxide hybrid for adsorptive removal of methylene blue from water, *J. Macromol. Sci., Part A: Pure Appl. Chem.*, 2016, **53**, 276–281.
- 61 Y. Lin, S. Wu, X. Li, X. Wu, C. Yang, G. Zeng, Y. Peng, Q. Zhou and L. Lu, Microstructure and performance of Z-scheme photocatalyst of silver phosphate modified by MWCNTs and Cr-doped SrTiO<sub>3</sub> for malachite green degradation, *Appl. Catal., B*, 2018, **227**, 557–570.
- 62 Y. K. Mohanta, S. K. Panda, R. Jayabalan, N. Sharma, A. K. Bastia and T. K. Mohanta, Antimicrobial, Antioxidant and Cytotoxic Activity of Silver Nanoparticles Synthesized by Leaf Extract of *Erythrina suberosa* (Roxb.), *Front. Mol. Biosci.*, 2017, **4**, 17.
- 63 M. Sathishkumar, A. T. Rajamanickam and M. Saroja, Characterization, antimicrobial activity and photocatalytic degradation properties of pure and biosynthesized zinc sulfide nanoparticles using plant extracts, *J. Mater. Sci.: Mater. Electron.*, 2018, **29**, 14200–14209.
- 64 M. F. Khan, A. H. Ansari, M. Hameedullah, E. Ahmad, F. M. Husain, Q. Zia, *et al.*, Sol-gel synthesis of thorn-like ZnO nanoparticles endorsing mechanical stirring effect and their antimicrobial activities: potential role as nano-antibiotics, *Sci. Rep.*, 2016, **6**, 27689.

