


 Cite this: *RSC Adv.*, 2020, 10, 43012

Improving the electrochemical performance of a natural molybdenite/N-doped graphene composite anode for lithium-ion batteries via short-time microwave irradiation†

 Shuonan Wang,^a Yun Hai,^a Bin Zhou,^b Hao Liu^{*b} and Libing Liao^{lib*}

In the present work, low-cost natural molybdenite was used to make a MoS₂/N-doped graphene composite through coulombic attraction with the aid of (3-aminopropyl)-triethoxysilane and the electrochemical performance was greatly improved by solvent-free microwave irradiation for tens of seconds. The characterization results indicated that most (3-aminopropyl)-triethoxysilane can decompose and release N atoms to further improve the N-doping degree in NG during the microwave irradiation. In addition, the surface groups of N-doped graphene were removed and the particle size of MoS₂ was greatly decreased after the microwave irradiation. As a result, the composite electrode prepared with microwave irradiation exhibited a better rate performance (1077.3 mA h g⁻¹ at 0.1C and 638 mA h g⁻¹ at 2C) than the sample prepared without microwave irradiation (1013.6 mA h g⁻¹ at 0.1C and 459.1 mA h g⁻¹ at 2C). Therefore, the present results suggest that solvent-free microwave irradiation is an effective way to improve the electrochemical properties of MoS₂/N-doped graphene composite electrodes. This work also demonstrates that natural molybdenite is a promising low-cost anode material for lithium-ion batteries.

 Received 10th September 2020
 Accepted 4th November 2020

DOI: 10.1039/d0ra07758e

rsc.li/rsc-advances

1. Introduction

Molybdenite (MoS₂), as a typical transition metal sulfide, is a promising anode material for lithium-ion batteries. It has a high theoretical specific capacity of 670 mA h g⁻¹.¹ After the initial cycle, MoS₂ decomposes and forms Li₂S and Mo atoms, and Mo atoms used to be considered to have no capacity.² But a lot of studies have shown that the reversible capacity of MoS₂ can reach 1000 mA h g⁻¹, and extra capacity arises from the Mo atoms accommodating six Li⁺ ions over the prolonged discharge process,³ so molybdenite has great potential in lithium-ion batteries. However, MoS₂ nanosheets are often subject to poor cycling stability and inferior rate capability because of their irreversible restacking, volume variation and poor electronic conductivity.^{4–6}

Integrating MoS₂ with N-doped graphene (NG) can combat these drawbacks.^{1,4,5,7–9} First, NG can form a network to alleviate the aggregation and volume expansion of nanomaterials.^{10,11} In addition, N-doping can improve the electrical conductivity of

carbon-based materials and offer ion transportation passages, which contribute to achieving a better rate performance during cycling.^{12–14} Furthermore, nitrogen doping in graphene can generate defects and active sites which enable the effective trapping of lithium polysulfides produced during lithiation of MoS₂, leading to improvement of the cycling performance.^{15–18} Previous work has shown that NG can significantly improve the electrochemical properties of MoS₂ anodes.^{1,19}

A compact interface between these two materials is essential for charge transfer during the charging/discharging processes.^{20,21} Because of the negative surface charge of MoS₂ and graphene,^{22–25} chemical modifiers or cross-linkers are usually used to ensure a compact interface through coulombic attraction^{7,26} or cross-linking.¹⁹ These chemicals can hinder the charge transfer process and can always be removed after the formation of the composite through traditional heating methods.^{7,19,26} For example, Li *et al.*²⁶ fabricated a 3D MoS₂@C/RGO composite through a surface-modification triggered self-assembly process. In order to disperse MoS₂ into GO solution and trigger the self-assembly process between MoS₂ and GO, polydopamine (PDA) coating of MoS₂ was carried out based on π–π stacking and hydrogen bonding interactions. A sintering process at 400 °C was applied to transform PDA into N-doped amorphous carbon. As a result, the composite had a high capacity and good rate performance.

In contrast to traditional heating methods, microwave irradiation is an energy-efficient and fast heating method for

^aBeijing Key Laboratory of Materials Utilization of Nonmetallic Minerals and Solid Wastes, National Laboratory of Mineral Materials, School of Materials Science and Technology, China University of Geosciences, Beijing, 100083, PR China. E-mail: clayl@cugb.edu.cn

^bSchool of Science, China University of Geosciences, Beijing, 100083, PR China. E-mail: liuhao1398@cugb.edu.cn

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d0ra07758e



material synthesis. Solvents usually need to be microwave absorbing and thermally conductive materials.^{27–31} For the last decade, solvent-free microwave irradiation synthesis methods have been gradually developed^{32–38} and some novel uses of solvent-free microwave irradiation have been explored such as microwave carbonization³⁹ and the synthesis of nanoparticles.³⁶ Previous studies showed that graphene can effectively absorb microwaves and generate a lot of heat and the temperature can rapidly rise above 1000 °C in a few seconds, and the particles loaded on the graphene can transform into nanoparticles from microparticles.³⁶ These facts inspire us to use this method to treat MoS₂/graphene composites or similar configurations to remove the chemical modifiers or cross-linkers and reduce graphene in a short time to improve the electrochemical performance of composite electrodes.

On the other hand, most reported MoS₂ anode materials are synthesized with a relatively high cost.⁴⁰ Nevertheless, molybdenite can be formed in nature and the reserves of molybdenite ore are abundant. High purity (>98.5%) but low cost natural molybdenite (\$14.50–18.20 per kg vs. ~\$140 per kg for synthesized MoS₂, Aladdin Co., >98%) can be obtained by using appropriate purification processes such as exfoliation^{41,42} and flotation.^{43,44} Several reports have demonstrated that natural molybdenite anodes can exhibit excellent electrochemical properties by size-controlling⁴⁵ and selecting a suitable binder.⁴⁴ Because the introduction of NG to form composites has many advantages, it is worth exploring the electrochemical properties of a natural molybdenite/NG composite electrode and the influence of microwave irradiation on this type of electrode.

In this work, we synthesized a natural molybdenite/NG composite and the natural molybdenite and NG were combined through coulombic attraction with the assistance of (3-aminopropyl)-triethoxysilane (APTES). This composite was further irradiated using microwaves for tens of seconds to enhance the interfacial interaction and the electronic conductivity through the removal of APTES and surface groups on NG. Therefore, the rate performance of this type of composite was greatly improved. This work not only demonstrated that the electrochemical performance of the MoS₂/NG composite or similar composites can be improved through solvent-free microwave irradiation for a short time, but also showed the potential application prospects of natural molybdenite ore as a promising low-cost anode material for lithium-ion batteries.

2. Experimental

2.1 Materials

Natural molybdenite ore was obtained from Guangzhou Haoyu stone craft firm. (3-Aminopropyl)-triethoxysilane (APTES) was purchased from Aladdin Industrial Corporation, Shanghai, China. N-doped graphene was supplied by Nanjing XFNano Materials Tech Co., Ltd.

2.2 Synthesis of MoS₂/NG and MoS₂/NG-MW

As shown in Fig. 1, natural molybdenite was crushed and sieved (50 mesh), and the sieved powder was ball-milled for 4 h at

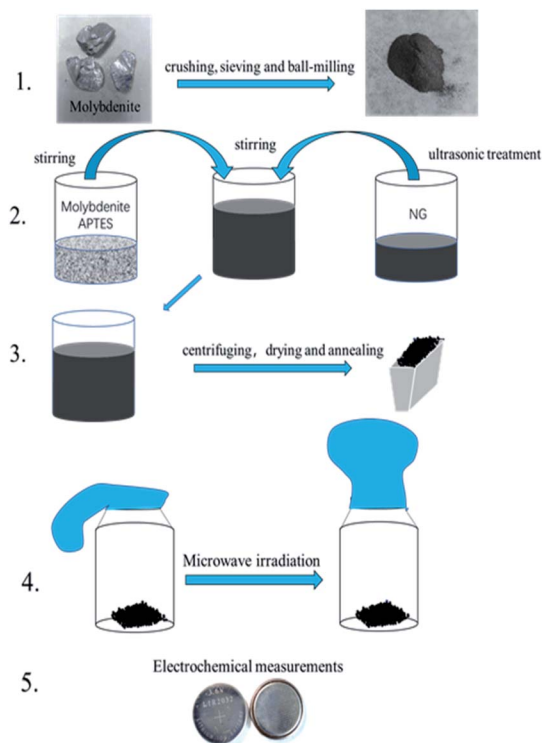


Fig. 1 Design idea for the MoS₂/NG-MW electrode material.

560 rpm in a planetary ball mill (QM-3SP2, Nanjing NanDa Instrument Plant). 0.1546 g molybdenite was dispersed in 50 ml ethanol–water mixture (volume ratio, 1 : 1), and the suspension was ultrasonicated for 5 min. 0.3 ml APTES was added to the molybdenite suspension under magnetic stirring for 1 h. 30 mg N-doped graphene was dispersed in 50 ml ethanol–water mixture (volume ratio, 1 : 1), and the suspension was ultrasonicated for 1 h. The two suspensions above were mixed under magnetic stirring for 1.5 h. The solid was obtained *via* centrifugation and dried at 60 °C for 12 h. Finally, the mixture was heated under argon flow to 250 °C with a heating rate of 5 °C min⁻¹ and maintained at this temperature for 2 h. This sample was marked as MoS₂/NG. Then, the MoS₂/NG was put in a glass bottle and sealed with a balloon in the glove box. The bottle was put into a microwave oven (Midea, M1-L213B, 700 W) on full power for 30 s. This sample was marked as MoS₂/NG-MW.

2.3 Characterization

The structural characteristics of the as-prepared samples were investigated by X-ray diffraction (XRD, D8 Advance, Bruker, Germany) with Cu K α radiation ($\lambda = 0.15406 \text{ \AA}$) at a voltage of 40 kV and a current of 100 mA, as well as X-ray photoelectron spectroscopy (XPS, K-Alpha, Thermo Scientific, America). The Raman spectra were obtained using a Laser Micro-Raman Spectrometer (Raman, Labram HR Evolution, Horiba Jobin Yvon, France) with a 532 nm laser. Fourier transform infrared spectra (FT-IR, Spectrum One, PerkinElmer, America) were obtained using the KBr pellet method. The morphology and



composition information were characterized by scanning electron microscopy (FESEM, MERLIN VP Compact, ZEISS, Germany) with energy-dispersive spectroscopy (EDS), transmission electron microscopy (TEM, FEI G2 F20 S-TWIN TMP, America) and thermogravimetric analysis (TGA, TGA/DSC-1, Mettler-Toledo, Switzerland) carried out at a heating rate of $10\text{ }^{\circ}\text{C min}^{-1}$ from 25 to $700\text{ }^{\circ}\text{C}$.

2.4 Electrochemical measurements

CR2032 coin-type lithium half-cells were assembled in a glove box filled with a highly pure Ar atmosphere (O_2 and H_2O levels <0.5 ppm), using metallic lithium as the counter electrode with a polypropylene separator (Celgard 2000), and 1 M LiPF_6 in ethylene carbonate (EC) and dimethyl carbonate (DMC) (volume ratio, 1 : 1) (provided by Nanjing Mojiesi Energy Technology Co., Ltd) as the electrolyte. The anode preparation was mixed with 90% $\text{MoS}_2/\text{NG-MW}$ and 10% binder (sodium alginate) additive, using deionized water as the solvent for blending the mixture. Then, the homogenous slurry was uniformly painted on copper foil and subsequently dried at $60\text{ }^{\circ}\text{C}$ for 12 h in a vacuum oven before obtaining the final working electrode. The pristine MoS_2 electrode was made using 70% molybdenite, 20% conductive agent (acetylene black) and 10% binder (sodium alginate) additive. The mass loading of active material (MoS_2) was $\sim 1.0\text{ mg cm}^{-2}$. The half-cells were allowed to stand for 12 h before the electrochemical measurements. The electrochemical impedance spectroscopy (EIS) tests were performed on an electrochemical workstation (Ivium-Vertex, Ivium Technologies, Holland) in the frequency range from 0.1 Hz to 100 kHz. The cyclic voltammetry (CV) was performed on an electrochemical work station (CS150, CorrTest, China) in the voltage range 3.0–0.1 V at a scan rate of 5 mV s^{-1} . The

galvanostatic charge/discharge tests and rate performance were carried out on a battery testing system (CT-4008, Neware, China).

3. Results and discussion

The phase identification was carried out by X-ray Powder Diffraction (XRD). As shown in Fig. 2(a), there are 9 peaks at 14.4° , 32.7° , 33.5° , 35.9° , 39.5° , 44.2° , 49.8° , 58.3° and 60.1° . All the diffraction peaks can be matched to the standard card of 2H- MoS_2 (JCPDS no. 37-1492), indicating that the primary component of the three samples is 2H- MoS_2 . Compared with pristine MoS_2 , the relative intensities of the diffraction peaks of the (002) planes of MoS_2/NG and $\text{MoS}_2/\text{NG-MW}$ are lower, indicating that the degree of preferred orientation of MoS_2 in these two samples decreased. On the other hand, the diffraction peak of NG is very weak because of the low content of NG in MoS_2/NG and $\text{MoS}_2/\text{NG-MW}$.

The detailed morphology and layer structure of the materials were investigated by SEM. As shown in Fig. 2(b), the pristine MoS_2 is an aggregate of layered MoS_2 and the particle size is 2–5 μm . As shown in Fig. 2(c) and the EDS analysis of MoS_2/NG , the atomic ratio of S to Mo is 2.02 : 1, which is consistent with the atomic ratio of MoS_2 . But in Fig. 2(d) and the EDS analysis of $\text{MoS}_2/\text{NG-MW}$, the atomic ratio of S to Mo is 1.53 : 1, indicating that MoS_2 decomposed and this caused the loss of S. As shown in Fig. 2(c) and (d), MoS_2 is interspersed with NG, the composite presents a flower-like structure and the MoS_2 particles in the composite material do not show agglomeration. The surface modification with APTES results in the presence of amino groups on the MoS_2 surface, and the electrostatic attraction between the amino groups and graphene reduced the

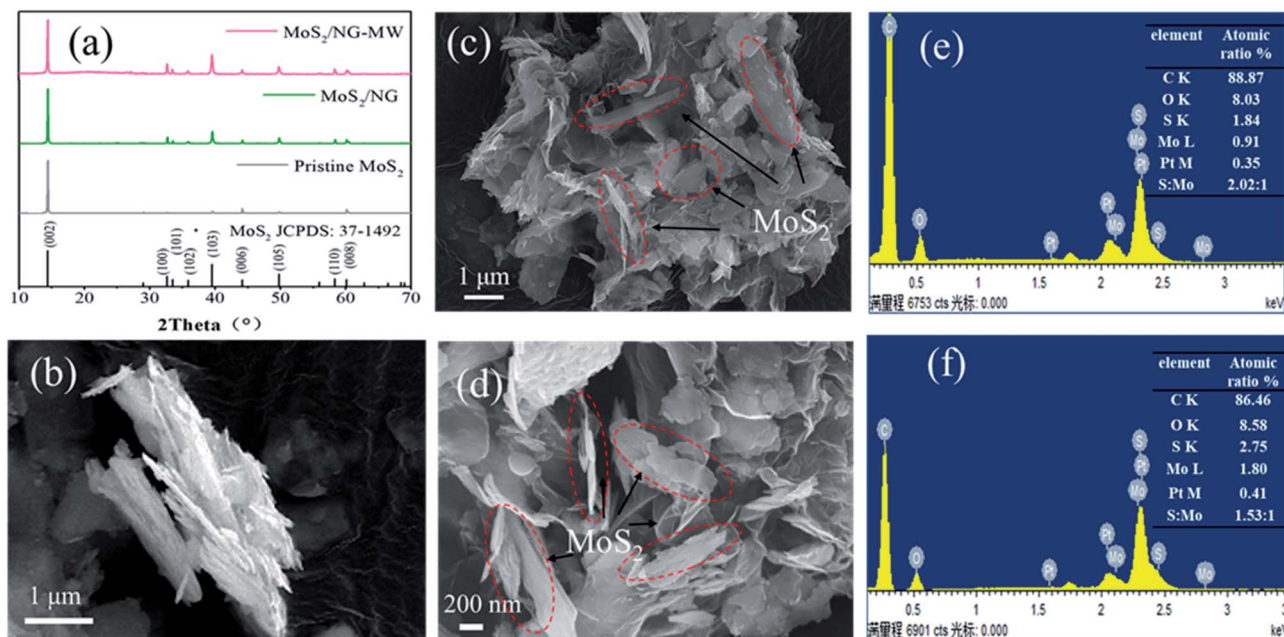


Fig. 2 (a) XRD patterns of pristine MoS_2 , MoS_2/NG and $\text{MoS}_2/\text{NG-MW}$; SEM images of (b) pristine MoS_2 , (c) MoS_2/NG and (d) $\text{MoS}_2/\text{NG-MW}$; EDS spectra of (e) MoS_2/NG and (f) $\text{MoS}_2/\text{NG-MW}$.



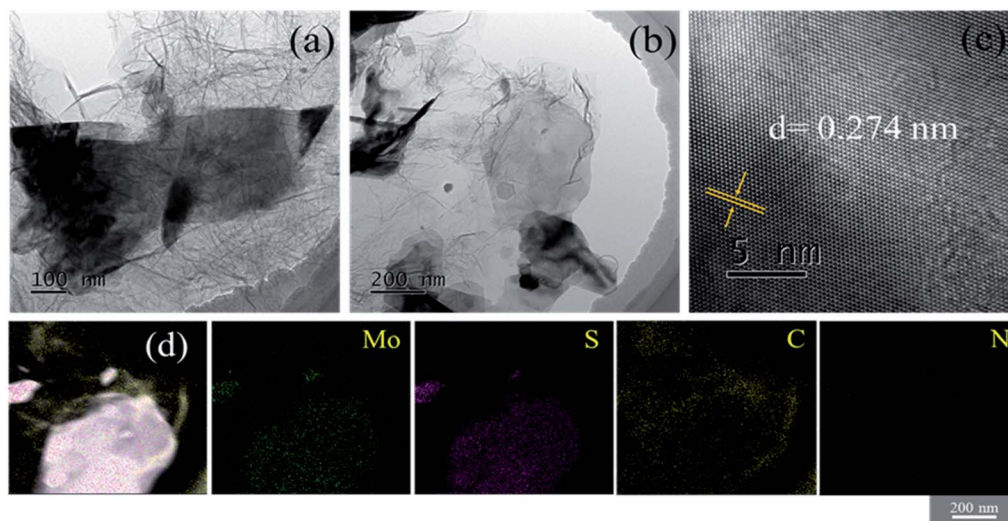


Fig. 3 The (a) and (b) TEM images, (c) HRTEM image and (d) STEM and element mapping images of MoS₂/NG-MW.

agglomeration.⁴⁶ The preferential orientation of MoS₂ is weak, which is consistent with the XRD pattern. By comparing Fig. 2(c) and (d), it can be clearly observed that after microwaving, the particle size of MoS₂ decreased from 2–5 μm to 0.5–1 μm.

Besides, the existence of microspheres in MoS₂/NG-MW also indicates that some MoS₂ decomposed and recombined.

The structural information was further revealed by TEM and the results are shown in Fig. 3. It can be clearly observed that there are MoS₂ nanosheets with particle sizes ranging from

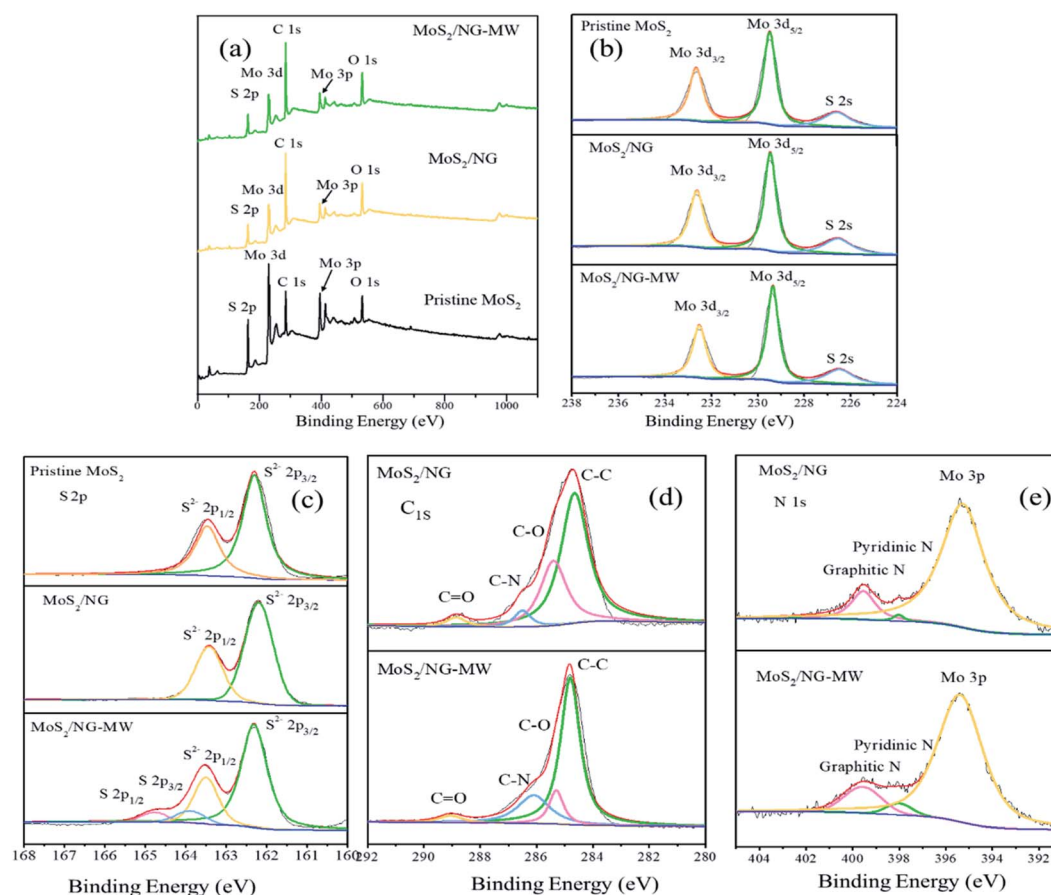


Fig. 4 (a) Total spectra, (b) Mo 3d, (c) S 2p, (d) C 1s, (e) N 1s high-resolution XPS spectra of pristine MoS₂, MoS₂/NG and MoS₂/NG-MW.



several hundred nanometers to one micrometer (Fig. 3(a) and (b)). The high-resolution transmission electron microscopy (HRTEM) image of MoS₂/NG-MW is displayed in Fig. 3(c) and the interplanar spacing is 0.274 nm which corresponds to the (100) plane of 2H-MoS₂. Fig. 3(d) shows the elemental distributions of Mo, S, C and N elements, revealing that the MoS₂ (bright parts in the STEM image) was wrapped in graphene (gray parts in the STEM image). Therefore, the above TEM results agree with the previous SEM and XRD results.

Furthermore, XPS spectra were used to distinguish the elements' oxidation states and the results are shown in Fig. 4. Mo, S, C and O are seen in the total spectra in Fig. 4(a), but the peak of N (~399 eV) cannot be observed in the total spectra because of the presence of a nearby strong Mo 3p peak (~395 eV). According to the Mo 3d spectra of pristine MoS₂, MoS₂/NG and MoS₂/NG-MW in Fig. 4(b), the three peaks at 232.6, 229.4 and 226.5 eV are attributed to Mo 3d_{3/2}, Mo 3d_{5/2}, and S 2s, respectively, corresponding with 2H-MoS₂.⁴⁷ The S 2p spectra of pristine MoS₂, MoS₂/NG and MoS₂/NG-MW are shown in Fig. 4(c), and the two peaks at 162.2 and 163.4 eV correspond to the S 2p_{3/2} and S 2p_{1/2} states of MoS₂.⁴⁷ But in the spectrum of MoS₂/NG-MW, there are two new peaks at 164.1 and 164.9 eV which correspond to the S 2p_{3/2} and S 2p_{1/2} states of elemental S, indicating that microwave irradiation caused a high temperature so that some of the MoS₂ decomposed and elemental S was produced. Due to the low content of elemental S, the diffraction peak of elemental S does not appear in the XRD pattern. The C 1s spectrum is depicted in Fig. 4(d), and there are four peaks at 284.8, 285.5, 286.6 and 288.5 eV which correspond with C-C, C-O, C-N, and C=O, respectively.^{16,48,49} The C-O (285.5 eV) peak area of MoS₂/NG-MW is smaller than that of MoS₂/NG, and the C-N (286.6 eV) peak area of MoS₂/NG-MW is larger than that of MoS₂/NG.

At the same time, the peaks at 398.5 and 401.4 eV in the high-resolution N 1s spectrum (Fig. 4(e)) can be attributed to the pyridinic N and graphitic N.^{1,50} The area of these two peaks is larger for MoS₂/NG-MW than MoS₂/NG, which coincides with the change in the C-N peak area. These results suggest that the functional groups on the NG surface were consumed but the N-doping degree was enhanced during microwave irradiation. They also demonstrate that the APTES decomposed and the released N atoms entered the NG layer during microwave irradiation.

The FT-IR spectra are shown in Fig. 5(a), and the FT-IR spectrum of MoS₂/NG shows a broad absorption band at 3234 cm⁻¹, which can be assigned to the O-H stretching vibration arising from the hydroxyl groups of the NG sheets.⁵¹ This peak disappeared after microwave irradiation, indicating that NG is reduced during the process of microwave irradiation. The peaks at 3065 cm⁻¹, 1662 cm⁻¹ and 1039 cm⁻¹ are associated with the N-H stretching vibrations of amino groups, N-H bond bending of amino groups and Si-O-C,⁴⁷ and are ascribed to the APTES. Nevertheless, the N-H peaks almost disappear and the intensity of the Si-O-C peak greatly decreases in MoS₂/NG-MW, indicating that most of the APTES decomposed during the process of microwave irradiation. The FT-IR results agree with the previous XPS results.

The structural features of the as-obtained samples were further explored through Raman spectroscopy. As shown in Fig. 5(b), the two distinct Raman peaks at 384 cm⁻¹ and 409 cm⁻¹ are attributed to the typical E_{2g}¹ and A_{1g} vibration modes of hexagonal MoS₂ crystals. There is no difference in peak separation (24.86 cm⁻¹) but the relative peak intensity ratios of A_{1g} and E_{2g}¹ provide important information on the crystallinity and degree of order of MoS₂. The A_{1g}/E_{2g}¹ values for MoS₂/NG and MoS₂/NG-MW are 1.36 and 1.25 respectively, suggesting that MoS₂/NG has better crystallinity. For the D band and G band of NG, the D band is associated with defects and the G band corresponds to the stretching mode of sp² bonded carbon.⁵² The ratio between the D band and G band decreased from 1.39 to 0.97 after microwave irradiation, suggesting that oxygen functional groups on the NG surface were removed during this process. This coincides with the results of FT-IR and XPS.

In order to know the amount of each component in the sample, TGA was performed and the results are shown in Fig. 5(c). The main temperature range for weight loss is 400–500 °C. The weight loss of pristine MoS₂ is attributed to the oxidation of MoS₂ to MoO₃ and SO₂. And the weight losses of MoS₂/NG and MoS₂/NG-MW are attributed to the oxidation of MoS₂ and NG to MoO₃, SO₂ and CO₂. The remaining weights of pristine MoS₂, MoS₂/NG and MoS₂/NG-MW were 89.1%, 68.1% and 65.4%, respectively, after heating to 700 °C. The mass fraction of MoS₂ is found to be around 76.3% and 73.4% in MoS₂/NG and MoS₂/NG-MW, respectively. The mass fraction of MoS₂ in MoS₂/NG-MW is lower than in MoS₂/NG, which is

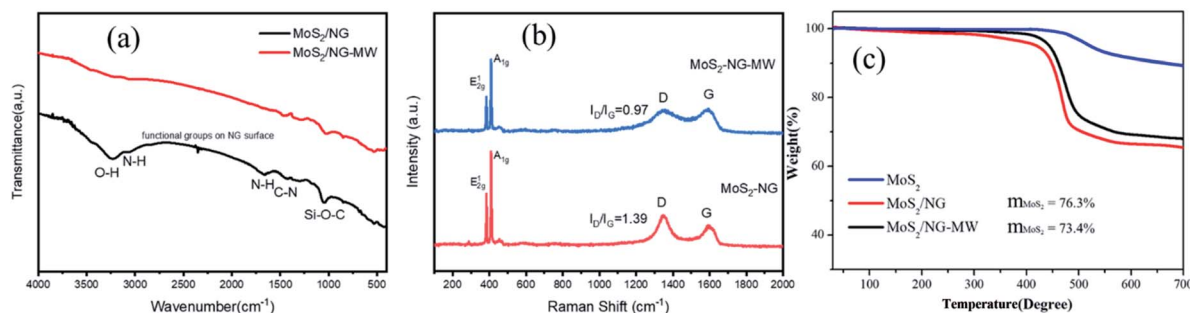


Fig. 5 (a) FT-IR and (b) Raman spectra of MoS₂/NG and MoS₂/NG-MW; (c) TGA curves of pristine MoS₂, MoS₂/NG and MoS₂/NG-MW.



associated with the decomposition of MoS_2 during microwave irradiation. Therefore, the TGA results coincide with the previous EDS and XPS results.

The CV curves of pristine MoS_2 and $\text{MoS}_2/\text{NG-MW}$ electrodes are shown in Fig. 6(a) and (b). For the first cyclic curve, two pronounced reductions at 0.85 V and 0.4 V are observed. The peak at 0.85 V can be ascribed to the intercalation of Li^+ into MoS_2 interlayers and the resulting 2H- MoS_2 to 1T- MoS_2 phase transition: $\text{MoS}_2 + x\text{Li}^+ + xe^- \rightarrow \text{Li}_x\text{MoS}_2$.⁵³ The peak at 0.4 V can

be attributed to the reduction of Li_xMoS_2 to Mo particles and Li_2S : $\text{Li}_x\text{MoS}_2 + (4-x)\text{Li}^+ + (4-x)e^- \rightarrow \text{Mo} + 2\text{Li}_2\text{S}$.¹ The oxidation peak at 2.35 V can be ascribed to the decomposition of Li_2S : $\text{Li}_2\text{S} - 2e^- \rightarrow 2\text{Li}^+ + \text{S}$.¹ In the subsequent cyclic curve, there are three distinct reduction peaks at 1.9 V, 1.1 V and 0.3 V, which can be assigned to the following three reactions: $2\text{Li}^+ + \text{S} + 2e^- \rightarrow \text{Li}_2\text{S}$, $\text{MoS}_2 + x\text{Li}^+ + xe^- \rightarrow \text{Li}_x\text{MoS}_2$, $\text{Li}_x\text{MoS}_2 + (4-x)\text{Li}^+ + (4-x)e^- \rightarrow \text{Mo} + 2\text{Li}_2\text{S}$. The charge-discharge profiles of the pristine MoS_2 and $\text{MoS}_2/\text{NG-MW}$ electrodes are shown in

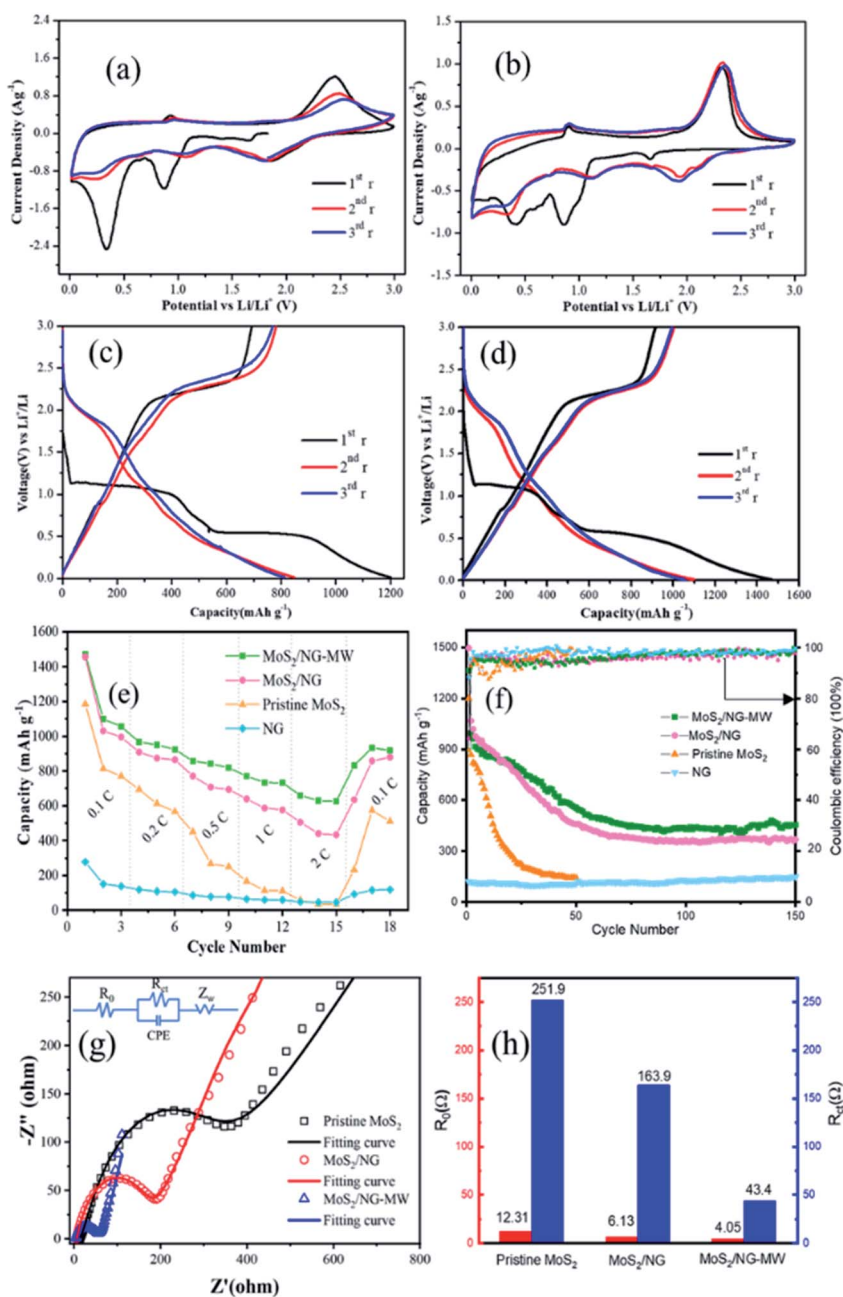


Fig. 6 CV curves of (a) pristine MoS_2 and (b) $\text{MoS}_2/\text{NG-MW}$ electrodes at a scanning rate of 0.5 mV s^{-1} ; the galvanostatic charge and discharge profiles of (c) pristine MoS_2 and (d) $\text{MoS}_2/\text{NG-MW}$ electrodes at 0.1C; (e) rate performance of pristine MoS_2 , MoS_2/NG and $\text{MoS}_2/\text{NG-MW}$ electrodes at various current densities; (f) cycling performance and coulombic efficiency of MoS_2 , MoS_2/NG and $\text{MoS}_2/\text{NG-MW}$ electrodes at 0.1C; (g) EIS curves of pristine MoS_2 , MoS_2/NG and $\text{MoS}_2/\text{NG-MW}$ electrodes; (h) the impedance parameters calculated from the equivalent circuit model fitting.



Fig. 6(c) and (d). As shown in Fig. 6(c) and (d), the two potential plateaus at 1.0 V and 0.5 V can be attributed to the intercalation of Li^+ into the MoS_2 interlayers and the reduction of Li_xMoS_2 to Mo particles and Li_2S . In the subsequent discharge curves, the two potential plateaus disappeared and a new potential plateau appeared at 1.9 V, in accordance with the formation of Li_2S . In the charge curves, the obvious potential plateau at about 2.3 V corresponds to the delithiation of Li_2S . Compared with the pristine MoS_2 electrode, the $\text{MoS}_2/\text{NG-MW}$ electrode has charge-discharge profiles with better repeatability, indicating that the $\text{MoS}_2/\text{NG-MW}$ electrode has better cycling performance. For the $\text{MoS}_2/\text{NG-MW}$ electrode, the discharge capacities are 1470, 1098 and 1056 mA h g^{-1} for the first three cycles. As for the pristine MoS_2 electrode, the discharge capacities are only 1185, 813 and 770 mA h g^{-1} for the first three cycles. The capacity loss of about 30% in the first cycle was the result of an irreversible process such as the formation of an inorganic solid electrolyte interphase (SEI) film and the irreversibility of Li_2S .³

Rate performances were tested at different current densities and the results are shown in Fig. 6(e). At rates of 0.1, 0.2, 0.5, 1 and 2C, the MoS_2/NG electrode exhibits average specific discharge capacities of 1013.6, 882.5, 723.8, 600.5 and 459.1 mA h g^{-1} , while the $\text{MoS}_2/\text{NG-MW}$ electrode exhibits better average specific discharge capacities of 1077.3, 956.7, 834, 745.5 and 638 mA h g^{-1} , respectively. In addition, the specific discharge capacities can recover to 879.5 and 918.4 mA h g^{-1} for the MoS_2/NG and $\text{MoS}_2/\text{NG-MW}$ electrodes when the current density goes back to 0.1C. In contrast, the capacity of the pristine MoS_2 electrode is only 509.4 mA h g^{-1} at the same rate.

It is obvious that the $\text{MoS}_2/\text{NG-MW}$ electrode has the best rate performance among these three electrodes. The cycling performances of pristine MoS_2 , MoS_2/NG and $\text{MoS}_2/\text{NG-MW}$ electrodes were measured at a rate of 0.1C. As shown in Fig. 6(f), the capacity of the pristine MoS_2 electrode decreased sharply for the first 30 cycles, and only 142.2 mA h g^{-1} was

preserved up to the 50th cycle. For the MoS_2/NG and $\text{MoS}_2/\text{NG-MW}$ electrodes, the capacities apparently decreased for the first 70 cycles, but the capacities remained stable for the next 80 cycles, which can be attributed to the fact that the flower-like structure could reduce the loss of active material. After 70 and 150 cycles, the specific discharge capacities of the MoS_2/NG electrode are 387.4 and 366.6 mA h g^{-1} , and those of the $\text{MoS}_2/\text{NG-MW}$ electrode are 459.8 and 453.7 mA h g^{-1} , respectively. The result confirms that $\text{MoS}_2/\text{NG-MW}$ has a more compact interface between MoS_2 and NG, so the loss of active material is reduced, leading to the better cycling performance of $\text{MoS}_2/\text{NG-MW}$. The initial coulombic efficiency is about 85% and quickly increases to above 95% after several cycles.

To confirm the difference in the electrochemical performance of the pristine MoS_2 , MoS_2/NG and $\text{MoS}_2/\text{NG-MW}$ electrodes, EIS tests were performed. The Nyquist plots and fitted equivalent circuit are shown in Fig. 6(g). The semicircular loop at the high-medium frequencies is related to resistance R_0 , electrode/electrolyte interface resistance (CPE) and charge transfer resistance (R_{ct}), and the sloped line at low frequencies represents the Warburg impedance (Z_w), which is connected to the Li^+ diffusion in the electrode materials.⁴⁵ The impedance parameters calculated from the equivalent circuit model fitting are shown in Fig. 6(h). The R_0 and R_{ct} of the $\text{MoS}_2/\text{NG-MW}$ electrode are 4.05 Ω and 43.4 Ω , which are much lower than those of the pristine MoS_2 electrode ($R_0 = 12.31 \Omega$, $R_{ct} = 251.9 \Omega$) and the MoS_2/NG electrode ($R_0 = 6.13 \Omega$, $R_{ct} = 163.9 \Omega$). This fact confirms that the electrical conductivity is improved. Nevertheless, the impedance spectra of the MoS_2/NG and $\text{MoS}_2/\text{NG-MW}$ electrodes become similar after tens of cycles (Fig. S1, ESI[†]).

We have compared the obtained results with the literature (Table S1, ESI[†]) and found that the $\text{MoS}_2/\text{NG-MW}$ composite possesses a good rate performance but the cycling performance is relatively poor. In order to know the reason for the poor cycling performance, SEM was performed and the results are

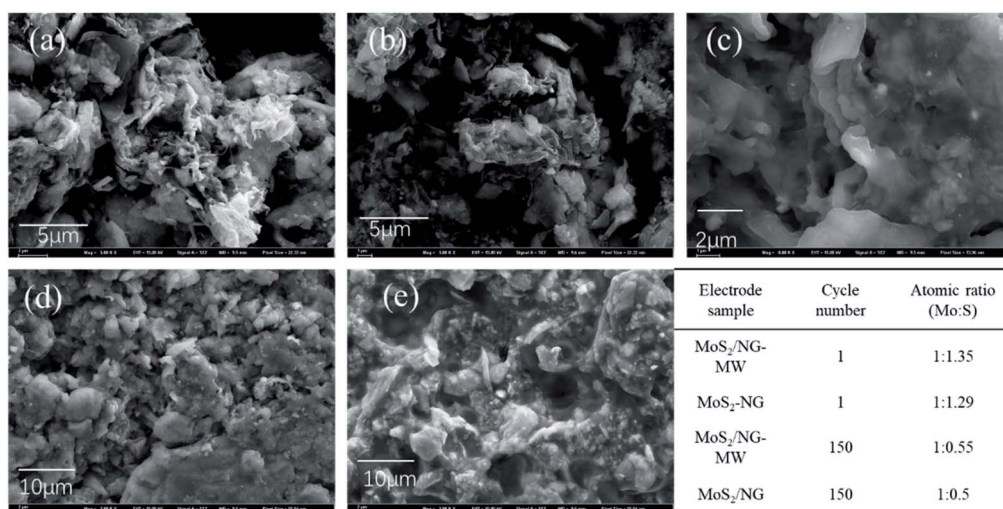


Fig. 7 SEM images of (a) $\text{MoS}_2/\text{NG-MW}$ and (b) MoS_2/NG electrodes after 1 cycle; SEM images of (c) and (d) $\text{MoS}_2/\text{NG-MW}$ and (e) MoS_2/NG electrodes after 150 cycles and EDS results of the MoS_2/NG and $\text{MoS}_2/\text{NG-MW}$ electrodes.



shown in Fig. 7. As shown in Fig. 7(a–e), it is hard to find the layered structure of MoS₂ after 150 cycles, and a thick SEI film can be observed on the surface of the electrode. According to the EDS results, the content of sulfur in the MoS₂/NG and MoS₂/NG-MW electrodes greatly decreases after 150 cycles. According to the CV results and other reports,² the reaction processes of MoS₂-based anode materials are similar to those of Li-S batteries after the first several cycles. Therefore, the problem of polysulfide dissolution has a great impact on the cycling stability of the electrodes. After long-term cycling, the content of sulfur in the MoS₂/NG and MoS₂/NG-MW electrodes greatly decreases due to this problem, leading to the poor cycling performance of these two electrodes. In addition, the difference between the MoS₂/NG and MoS₂/NG-MW electrodes becomes small after tens of cycles, leading to similar impedance of these two electrodes. Several measures can be taken to improve the electrochemical performance of our samples. For example, other binders, such as carboxymethyl cellulose (CMC), may be more suitable than sodium alginate for a MoS₂-based anode.^{44,45} In addition, adding some porous or surface polarization materials, which can trap the soluble polysulfide, in the composite electrode or separator may also lead to an improvement of the cycling stability.

Based on the above results, it can be concluded that microwave irradiation can greatly improve the rate performance and cycling performance of the MoS₂/NG composite. Firstly, the APTES can decompose and the released N atoms enter into the NG layer during microwave irradiation. Therefore, MoS₂/NG-MW has a more compact interface and the N-doping degree is enhanced, which are beneficial for the charge transfer during the charging/discharging processes. Secondly, the functional groups on the NG surface are removed during microwave irradiation and this can further improve the electronic conductivity of the composite. Thirdly, the particle size of MoS₂ decreases from 2–5 μm to 0.5–1 μm and the transfer path for ions and electrons can be greatly shortened during cycling. Therefore, the rate performance of the MoS₂/NG-MW electrode has been improved by microwave irradiation.

4. Conclusions

In summary, a natural molybdenite/NG composite was synthesized with the assistance of APTES, and the electrochemical performance of the composite was improved *via* short-time microwave irradiation. The influence of microwave irradiation was verified and the results indicated that part of the MoS₂ was decomposed during microwave irradiation and its particle size decreased from 2–5 μm to 0.5–1 μm, which can greatly shorten the transfer paths for ions and electrons during cycling. Besides, most of the APTES decomposed and the released N atoms entered into the NG layer during microwave irradiation, which is beneficial for charge transfer during the charging/discharging processes. Furthermore, the functional groups on the NG surface are consumed during microwave irradiation and this can further improve the electronic conductivity of the composite. As a result, MoS₂/NG-MW exhibited a good rate performance (1077.3 mA h g⁻¹ at 0.1C and 638 mA h g⁻¹ at 2C)

and good cycling performance (459.8 and 453.7 mA h g⁻¹ after 70 and 150 cycles at 0.1C), which are superior to those of MoS₂/NG. This work not only suggested that short-time solvent-free microwave irradiation could improve the electrochemical performance of the MoS₂/NG composite or similar NG composites, but also indicated that natural molybdenite ore is a promising low-cost anode material for lithium-ion batteries.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work is supported by the Fundamental Research Funds for the Central Universities (No. 2652019108) and the National Natural Science Foundation of China (No. 21875223).

Notes and references

- 1 B. Chen, Y. Meng, F. He, E. Liu, C. Shi, C. He, L. Ma, Q. Li, J. Li and N. Zhao, *Nano Energy*, 2017, **41**, 154–163.
- 2 T. Stephenson, Z. Li, B. Olsen and D. Mitlin, *Energy Environ. Sci.*, 2014, **7**, 209–231.
- 3 L. Wang, Q. Zhang, J. Zhu, X. Duan, Z. Xu, Y. Liu, H. Yang and B. Lu, *Energy Storage Mater.*, 2019, **16**, 37–45.
- 4 K. Chang, D. Geng, X. Li, J. Yang, Y. Tang, M. Cai, R. Li and X. Sun, *Adv. Energy Mater.*, 2013, **3**, 839–844.
- 5 J. Jiao, K. Du, Y. Wang, P. Sun, H. Zhao, P. Tang, Q. Fan, H. Tian, Q. Li and Q. Xu, *Mater. Chem. Phys.*, 2020, **240**, 122169.
- 6 F. Tu, Y. Han, Y. Du, X. Ge, W. Weng, X. Zhou and J. Bao, *ACS Appl. Mater. Interfaces*, 2019, **11**, 2112–2119.
- 7 K. Chang and W. Chen, *ACS Nano*, 2011, **5**, 4720–4728.
- 8 L. Ma, J. Ye, W. Chen, D. Chen and J. Yang Lee, *Nano Energy*, 2014, **10**, 144–152.
- 9 B. Yu, Y. Chen, Z. Wang, D. Chen, X. Wang, W. Zhang, J. He and W. He, *J. Power Sources*, 2020, **447**, 227364.
- 10 D. Zhou, W.-L. Song, X. Li, L.-Z. Fan and Y. Deng, *J. Alloys Compd.*, 2017, **699**, 730–737.
- 11 N. Wu, W. Du, X. Gao, L. Zhao, G. Liu, X. Liu, H. Wu and Y. B. He, *Nanoscale*, 2018, **10**, 11460–11466.
- 12 X. Tang, G. Wen and Y. Song, *Appl. Surf. Sci.*, 2018, **436**, 398–404.
- 13 X. Ge, S. Liu, M. Qiao, Y. Du, Y. Li, J. Bao and X. Zhou, *Angew. Chem., Int. Ed.*, 2019, **58**, 14578–14583.
- 14 X. Zhou, L. Yu and X. W. D. Lou, *Adv. Energy Mater.*, 2016, **6**, 1600451.
- 15 D. Su, M. Cortie and G. Wang, *Adv. Energy Mater.*, 2017, **7**, 1602014.
- 16 X. Li, Y. Bai, M.-S. Wang, G. Wang, Y. Ma, L. Li, B. Xiao and J. Zheng, *Sustainable Energy Fuels*, 2019, **3**, 1427–1438.
- 17 C. Li, X.-L. Sui, Z.-B. Wang, Q. Wang and D.-M. Gu, *Ceram. Int.*, 2018, **44**, 13419–13425.
- 18 S.-K. Liu, X.-B. Hong, Y.-J. Li, J. Xu, C.-M. Zheng and K. Xie, *Chin. Chem. Lett.*, 2017, **28**, 412–416.



- 19 S. Xia, Y. Wang, Y. Liu, C. Wu, M. Wu and H. Zhang, *Chem. Eng. J.*, 2018, **332**, 431–439.
- 20 X. Liu, Q. Yang, M. Mi, W. Kong, Y. Ge, J. Ma and J. Hu, *J. Alloys Compd.*, 2019, **800**, 99–106.
- 21 W. Zhang, S. Fang, N. Wang, J. Zhang, B. Shi, Z. Yu and J. Yang, *Inorg. Chem. Front.*, 2020, **7**, 2487–2496.
- 22 J. H. Lee, S. H. Kwon, S. Kwon, M. Cho, K. H. Kim, T. H. Han and S. G. Lee, *Nanomaterials*, 2019, **9**, 268.
- 23 M. Morant-Giner, I. Brotons-Alcázar, N. Y. Shmelev, A. L. Gushchin, L. T. Norman, A. N. Khlobystov, A. Alberola, S. Tatay, J. Canet-Ferrer, A. Forment-Aliaga and E. Coronado, *Chem.–Eur. J.*, 2020, **26**, 6670–6678.
- 24 C. Zhao, R. Wang, Y. Zhang, L. Chen, T. Li, X. Deng, P. Zhang and X. Lu, *Electrochim. Acta*, 2019, **320**, 134591.
- 25 Y. Fang, Q. Huang, P. Liu, J. Shi and G. Xu, *Colloids Surf., A*, 2018, **540**, 112–122.
- 26 S. Li, P. Liu, X. Huang, Y. Tang and H. Wang, *J. Mater. Chem. A*, 2019, **7**, 10988–10997.
- 27 E. Alsharaeh, F. Ahmed, Y. Aldawsari, M. Khasawneh, H. Abuhimad and M. Alshahrani, *Sci. Rep.*, 2016, **6**, 29854.
- 28 E.-S. M. Duraia, A. Fahami and G. W. Beall, *J. Electron. Mater.*, 2018, **47**, 7288–7295.
- 29 S. Shi, X. Hua and H. Guo, *Ceram. Int.*, 2018, **44**, 13495–13501.
- 30 Y. Aldawsari, Y. Mussa, F. Ahmed, M. Arsalan and E. Alsharaeh, *Materials*, 2019, **12**, 2248.
- 31 Z. W. Lu, Y. H. Wang, Z. Dai, X. P. Li, C. Y. Zhang, G. Z. Sun, C. S. Gong, X. J. Pan, W. Lan, J. Y. Zhou and E. Q. Xie, *Electrochim. Acta*, 2019, **325**, 134920.
- 32 D. Voiry, J. Yang, J. Kupferberg, R. Fullon, C. Lee, H. Y. Jeong, H. S. Shin and M. Chhowalla, *Science*, 2016, **353**, 1413–1416.
- 33 B. K. Barman and K. K. Nanda, *ACS Sustainable Chem. Eng.*, 2018, **6**, 4037–4045.
- 34 J. Xu, R. Zhang, S. Lu, H. Liu, Z. Li, X. Zhang and S. Ding, *Nanotechnology*, 2018, **29**, 305708.
- 35 J. A. Rudd, C. E. Gowenlock, V. Gomez, E. Kazimierska, A. M. Al-Enizi, E. Andreoli and A. R. Barron, *J. Mater. Sci. Technol.*, 2019, **35**, 1121–1127.
- 36 S. Xu, G. Zhong, C. Chen, M. Zhou, D. J. Kline, R. J. Jacob, H. Xie, S. He, Z. Huang, J. Dai, A. H. Brozena, R. Shahbazian-Yassar, M. R. Zachariah, S. M. Anlage and L. Hu, *Matter*, 2019, **1**, 759–769.
- 37 S. Liu, P. Yan, H. Li, X. Zhang and W. Sun, *Front. Chem.*, 2020, **8**, 104.
- 38 Y. Lin, D. W. Baggett, J.-W. Kim, E. J. Siochi and J. W. Connell, *ACS Appl. Mater. Interfaces*, 2011, **3**, 1652–1664.
- 39 Q. Shi, D. Liu, Y. Wang, Y. Zhao, X. Yang and J. Huang, *Small*, 2019, **15**, 1901724.
- 40 S. Chen, J. Gao, B. M. Srinivasan and Y.-W. Zhang, *Acta Phys.-Chim. Sin.*, 2019, **35**, 1119–1127.
- 41 W. Zhao, T. Jiang, Y. Shan, H. Ding, J. Shi, H. Chu and A. Lu, *Nanomaterials*, 2018, **8**, 843.
- 42 N. Savjani, E. A. Lewis, R. A. D. Patrick, S. J. Haigh and P. O'Brien, *RSC Adv.*, 2014, **4**, 35609–35613.
- 43 P. F. A. Braga, A. P. Chaves, A. B. Luz and S. C. A. França, *Int. J. Miner. Process.*, 2014, **127**, 23–27.
- 44 S. Li, H. Tang, P. Ge, F. Jiang, J. Zhou, C. Zhang, H. Hou, W. Sun and X. Ji, *ACS Appl. Mater. Interfaces*, 2018, **10**, 6378–6389.
- 45 F. Jiang, S. Li, P. Ge, H. Tang, S. A. Khoso, C. Zhang, Y. Yang, H. Hou, Y. Hu, W. Sun and X. Ji, *Front. Chem.*, 2018, **6**, 389.
- 46 W. Chen, S. Qi, L. Guan, C. Liu, S. Cui, C. Shen and L. Mi, *J. Mater. Chem. A*, 2017, **5**, 5332–5341.
- 47 C. Chen, Y. He, G. Xiao, Y. Xia, H. Li and Z. He, *Appl. Surf. Sci.*, 2018, **444**, 511–521.
- 48 S. Tao, D. Wu, S. Chen, B. Qian, W. Chu and L. Song, *Chem. Commun.*, 2018, **54**, 8379–8382.
- 49 Z. Jing, X. Dai, X. Xian, Q. Zhang, H. Zhong and Y. Li, *Materials*, 2020, **13**, 2529.
- 50 J. Liu, A. X. Wei, M. Chen and X. Xia, *J. Mater. Chem. A*, 2018, **6**, 3857–3863.
- 51 T. Liu, X. Zhang, B. Li, J. Ding, Y. Liu, G. Li, X. Meng, Q. Cai and J. Zhang, *RSC Adv.*, 2014, **4**, 50765–50770.
- 52 P. Krawczyk, B. Gurzęda and A. Bachar, *Appl. Surf. Sci.*, 2019, **481**, 466–472.
- 53 Y. Miki, D. Nakazato, H. Ikuta, T. Uchida and M. Wakihara, *J. Power Sources*, 1995, **54**, 508–510.

