


 Cite this: *RSC Adv.*, 2020, 10, 43175

Preparation and catalytic properties of poly(methyl methacrylate)-supported Pd⁰ obtained from room-temperature, dark reduction of ionic aggregates of the unstable Pd²⁺ solution ionomer

 Jinqiang Tan, Huamei Zhu, Shasha Cao, Sisi Chen, Yuanfu Tian,^{ID} Dachuan Ding, Xuan Zheng, Chuanqun Hu, Tao Hu and Chonggang Wu^{ID*}

A poly(methyl methacrylate)-supported Pd⁰ nanocatalyst was successfully prepared from solution reaction of Pd(CH₃COO)₂ with a copolymer acid, poly(methyl methacrylate-*ran*-methacrylic acid) (MMA-MAA). The reaction was carried out in a benzene/methanol mixed solvent in the dark at room temperature (~25 °C) in the absence of a typical chemical reductant. There was coordination between the Pd⁰ nanoclusters and MMA-MAA, resulting in Pd⁰ nanoclusters being stably and uniformly dispersed in the MMA-MAA matrix, with an average particle size of ~2.5 ± 0.5 nm. Mechanistically, it can tentatively be proposed that PMMA-ionomerization of the Pd²⁺ ions produces intramolecular -2COO⁻-Pd²⁺ aggregate cross-links in the solution. On swelling of the chain-segments that are covalently bound *via* multiple C-C bonds, the resultant elastic forces cause instantaneous dissociation at the O-Pd coordination bonds to give transient bare (*i.e.*, uncoordinated), highly-oxidative Pd²⁺ ions and H⁺-associative carboxylate groups, both of which rapidly scavenge electrons and protons, respectively, of the active α-H atoms abstracted from the methanol molecules of the solvent to make Pd⁰ nanoclusters supported by the re-formed MMA-MAA. The MMA-MAA acid copolymer, without itself undergoing any permanent chemical change, serves as a mechanical activator or catalyst for the mechanochemical reduction of Pd(CH₃COO)₂ under mild conditions. Compared with traditional Pd/C catalysts, this Pd⁰ nanocatalyst exhibited more excellent catalytic efficiency and reusability in the Heck reaction between iodobenzene and styrene, and it could be easily separated. The supported Pd⁰ nanocatalyst prepared using this novel and simple preparation method may display high-efficiency catalytic properties for other cross coupling reactions.

 Received 11th October 2020
 Accepted 16th November 2020

DOI: 10.1039/d0ra08653c

rsc.li/rsc-advances

1. Introduction

The Pd⁰ nanocatalyst has good activity for applications including hydrogenation,¹ oxidation,^{2,3} and dehydrogenation reactions.⁴ It is mainly used in catalytic hydrogenation and oxidation processes in industries such as the petrochemical industry and also used for cross coupling reactions⁵ such as the Heck,^{6,7} Suzuki,^{8,9} and Stille¹⁰ reactions. For a long time, the amount of Pd used was second only to Pt. At the end of the 20th century, the amount of Pd used in catalysis exceeded that of Pt because of a sharp increase in the amount of catalyst used for automobile exhaust purification. Traditional Pd⁰ particles are susceptible to oxidation and aggregation, and it is difficult to separate and reuse them from the reaction system. This can cause product pollution and increase costs. Supported Pd⁰

catalysts have the potential to overcome these shortcomings, in particular, metal catalysts supported on polymer surfaces have become a topic of intense research interest because to their higher catalytic activity and stereoselectivity, better stability and reusability, and easier recyclability. In addition to polymers used as the support, ceramics¹¹⁻¹³ and organic-inorganic composites¹⁴⁻¹⁶ are also used as supports for Pd⁰ nanoclusters.

According to the reduction driving force in the reaction, the preparation methods for polymer-supported Pd⁰ catalysts are mainly divided into thermal decomposition of metal compounds,^{17,18} chemical reduction,^{19,20} ultrasonic radiation,²¹ microwave radiation,^{22,23} and light reduction.²⁴ In the metal compound thermal decomposition method, a composite precursor is obtained through the coordination action of the complex with different metal ions; then, the thermal decomposition method is used to separate the complex from the metal to obtain nanoparticles. The chemical reduction method uses a reducing agent, and the metal precursor oxidation-reduction reaction takes place to afford Pd⁰ nanoclusters. The ultrasonic radiation method uses ultrasonic waves to irradiate the

Hubei Provincial Key Laboratory of Green Materials for Light Industry, Collaborative Innovation Center of Green Light-weight Materials and Processing, School of Materials and Chemical Engineering, Hubei University of Technology, Wuhan, Hubei Province 430068, P. R. China. E-mail: cgwu@mail.hbut.edu.cn



material; the ultrasonic cavitation phenomenon produced by ultrasonic radiation of materials plays a role similar to heating and pressurization. When used as a chemical reaction, this ultrasonic cavitation phenomenon plays a role in providing the driving force for reduction, making it easier for the precursors to obtain electrons and a reduction reaction will occur. The microwave radiation method also essentially uses heating as the driving force for reduction. Compared with traditional heating, microwave radiation can heat the solvent uniformly and there is no heating after-effect; hence, the size distribution of the nanoparticles is more uniform. The mechanism of the light (visible light, ultraviolet light, X-ray, and γ -ray/electron pulse) reduction method is currently unclear. In a practical preparation process, two or more preparation methods are often used in combination.

In the above method for preparing a polymer-supported Pd⁰ catalyst, light or heat is involved in the reduction process. Photo-irradiation or heating appears to be a necessary factor for metal ions to be reduced. Based on this, a poly(methyl methacrylate-*ran*-12.1 mol% methacrylic acid) supported Pd⁰ nanocatalyst (Pd⁰/MMA-MAA) was prepared by the solution reduction method in the dark (without photo-irradiation) under room temperature (without heating) in our laboratory.²⁵ Transmission Electron Microscopy (TEM), wide-angle X-ray scattering (WAXS), and Fourier transform infrared (FT-IR) spectroscopy were used to confirm the successful preparation of the product. The prepared Pd⁰ nanoclusters were uniformly distributed on the support (MMA-MAA), and the average particle size (diameter) was in the range of 2.5 ± 0.5 nm. The Pd⁰/MMA-MAA had excellent catalytic properties and reusability in the Heck reaction between iodobenzene and styrene.

2. Materials and methods

2.1 Materials

An amorphous copolymer acid, poly(methyl methacrylate-*ran*-12.1% methacrylic acid) (MMA-12.1% MAA) with an M_w of $\sim 1 \times 10^5$ was supplied by Polysciences, in which 12.1% refers to the mole percent of the MAA units in the copolymer. Palladium(II) acetate (Pd(CH₃COO)₂) and iodobenzene were purchased from Sigma-Aldrich and Aladdin respectively, these two chemical reagents had a purity of $\geq 98\%$. Benzene, styrene, *N,N*-dimethylformamide (DMF), ether, toluene, methanol, and acetone with purity $\geq 99.5\%$ were purchased from Sinopharm Shanghai Chemical Reagents Co., Ltd., China. Triethylamine (Et₃N) and anhydrous sodium sulfate, both with purity $\geq 99\%$, were also purchased from Sinopharm Shanghai Chemical Reagents Co., Ltd., China.

The PMMA copolymer acid (*i.e.*, MMA-12.1% MAA) and styrene were purified before use. MMA-12.1% MAA was purified by precipitation from a mixed solvent of benzene/methanol (9/1 v/v) into an excess of methanol (at least 20 times the volume of the solvent), followed by Büchner filtration, washing with methanol several times, and vacuum drying at 60 °C for *ca.* 48 h. For the styrene purification process, it was extracted three times with a 5 mol% NaOH aqueous solution, then washed several times with distilled water, and finally an appropriate amount of

anhydrous sodium sulfate was added to the washed styrene followed by filtering after standing overnight. The other chemicals (*i.e.*, Pd(CH₃COO)₂, iodobenzene, benzene, styrene, DMF, ether, toluene, methanol, acetone, Et₃N, and anhydrous sodium sulfate) were used as received without further purification.


2.2 Sample preparation

The Pd⁰/MMA-MAA catalyst was prepared by solution reaction at room temperature without strong light stimulation. MMA-12.1% MAA and Pd(CH₃COO)₂ were mixed in solution at room temperature (air-conditioned at ~ 25 °C) with a self-made dark box covering the entire reaction apparatus to minimize exposure to light after mixing. The possible reactions in the mixed solution include the neutralization reaction of MAA carboxyls and Pd(CH₃COO)₂ to form a Pd-salt MMA-MAA ionomer and Pd²⁺ ion reduction from the Pd-salt ionomer and Pd(CH₃COO)₂ to Pd atoms (Pd atoms would aggregate into Pd nanoclusters). Four samples with reaction times of 20 min, 4 h, 12 h, and 24 h were prepared for comparison. The potential neutralization reaction of the MMA-MAA with Pd(CH₃COO)₂ can schematically be shown by Scheme 1.

To convert as much of the carboxylic-acid groups to Pd-carboxylate groups as possible in the neutralization reaction, the mole ratio of the MMA-MAA carboxyls to Pd(CH₃COO)₂ was controlled at 1/1.05; *i.e.*, the amount of Pd(CH₃COO)₂ actually used was 5% more than the amount (mol) calculated by the stoichiometric proportion of the acid content (c_{acid}) (mol) for a certain mass of MMA-MAA. Therefore, the actual c_{acid} (mol%) of the purified MMA-MAA must be determined by acid-base titration before it is used in the solution reaction for accurate measurements. A NaOH aqueous solution with a molar concentration of $\sim 5.0 \times 10^{-2}$ M was prepared and placed in a basic burette; its exact concentration was titrated *in situ* with a precise amount of potassium-biphthalate standard of *ca.* 1.0×10^{-2} g mL⁻¹ in distilled water in an Erlenmeyer flask in advance. Then, a small amount of the purified MMA-MAA was dissolved in another tetrahydrofuran/water (9/1 v/v) solution to form a solution with a concentration of $\sim 2.0 \times 10^{-2}$ g mL⁻¹. It was then titrated with the NaOH aqueous solution, using phenolphthalein as an indicator. The above operation was repeated three times and the average value was taken to determine that the actual c_{acid} (mol%) of the purified MMA-MAA was 12.1 mol%.

Finally, with a MAA-carboxyl/Pd(CH₃COO)₂ mole ratio of 1/1.05, the solution reaction was carried out in the dark at room temperature: 0.0884 g of maroon Pd(CH₃COO)₂ was stirred with 10 mL of methanol at room temperature for 10 min in a 25 mL stoppered round-bottom flask; the resulting maroon solution (from dissolved Pd(CH₃COO)₂ in methanol) was decanted into a stirred colorless solution of 0.6000 g of MMA-MAA dissolved in 30 mL of benzene/methanol (9/1 v/v), contained in a 100 mL round-bottom flask, to form an orange reaction mixture; the mixture then was sealed, placed inside a home-made dark box to prevent light exposure, and stirred vigorously at room temperature for different durations ranging from 20 min to 24 h; the solution was subsequently was poured into a large



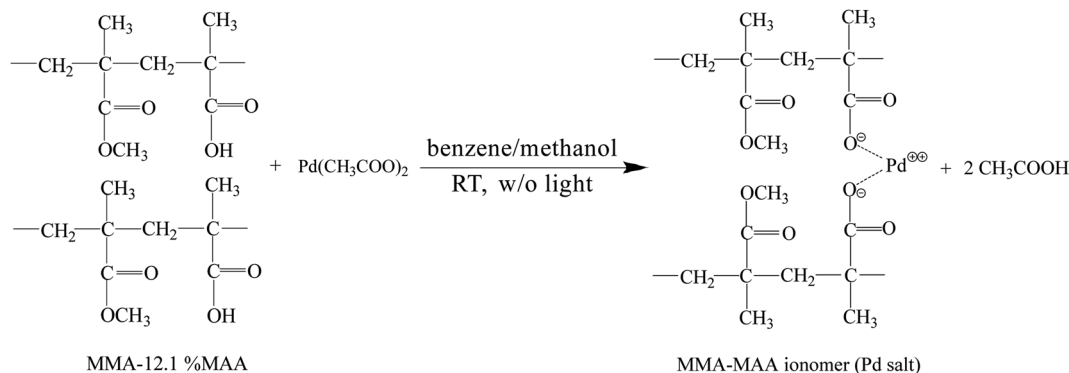

Scheme 1 The equation for the neutralization reaction between poly(methyl methacrylate-*ran*-12.1 mol% methacrylic acid) (MMA-12.1% MAA) and $\text{Pd}(\text{CH}_3\text{COO})_2$ to generate Pd-salt MMA-MAA ionomer in the dark (without photoirradiation) at room temperature ($\sim 25^\circ\text{C}$).

amount of methanol (at least 20 times the volume of the mixture) to precipitate the product; the powdery and/or fibrous product was filtered off with a Büchner funnel, followed by washing with methanol several times, then with acetone repeatedly to remove any residual $\text{Pd}(\text{CH}_3\text{COO})_2$, and finally again with methanol several times; the washed product was dried *in vacuo* at room temperature for at least 4 days.

2.3 Catalytic reaction of the sample

$\text{Pd}^0/\text{MMA-MAA}$ was used to catalyze the Heck reaction of iodobenzene and styrene to produce *trans*-stilbene and its catalytic properties were then explored. Styrene needs to be purified to remove the *tert*-butyl catechol polymerization inhibitor and other impurities before the catalytic reaction. First, 15 mL of styrene was measured with a 50 mL graduated cylinder and transferred to a 60 mL separatory funnel (covered with a stopper), followed by adding ~ 5 mL of 5 mol% NaOH aqueous solution to the separatory funnel. It was lightly shaken several times and then left to rest to separate the layers, and the lower solution layer was discarded. This was repeated three times; then, 5 mL of distilled water was added to the separatory funnel for washing, the lower liquid layer was discarded, and the washing was repeated several times until the lower liquid layer was tested to be neutral with a PH test paper. The washed upper liquid (styrene) was transferred to a 50 mL Erlenmeyer flask, then, 5 g of anhydrous sodium sulfate was added for drying and it was left to stand overnight.

The experimental process for the catalytic reaction can be summarized as follows. A 10 mL three-necked flask was charged with 0.1049 g of $\text{Pd}^0/\text{MMA-MAA}$, 0.3125 g of styrene, and 2.5 mL of DMF; it was then stirred vigorously for 5 min, then 2.5 mmol of iodobenzene and 3.75 mmol of Et_3N were added to the three-


necked flask and stirred at 100°C for 2 h. After the reaction was completed, the 10 mL three-necked flask was taken out and left to cool at room temperature for 30 min. After cooling, the mixture was separated with a simple funnel. The filtrate was diluted with 2.5 mL of distilled water and extracted twice with 5 mL of diethyl ether, and the organic extract was dried over anhydrous sodium sulfate. Then, a rotary evaporator (starting from room temperature and gradually increasing temperature to 90°C with a vacuum at ~ 0.09 MPa) was used to vacuum evaporate the organic extract and obtain the crude product. The crude product was then placed in a 120°C vacuum drying box for 48 h. The filtered solid ($\text{Pd}^0/\text{MMA-MAA}$) was washed with 2.5 mL of distilled water three times, then washed three times with 2.5 mL of toluene, dried in a fume hood for 24 h, and the catalyst was then transferred to a 120°C vacuum drying oven for 24 h. The dried $\text{Pd}^0/\text{MMA-MAA}$ was reused for the Heck reaction. The reaction equation of the iodobenzene and styrene is shown in Scheme 2.

3. Results and discussion

3.1 TEM evidence of Pd^0 -nanocluster formation

As shown in Scheme 1, MMA-MAA and $\text{Pd}(\text{CH}_3\text{COO})_2$ are likely to undergo a neutralization reaction to form the Pd-salt MMA-MAA ionomer under dark conditions at room temperature. Part of the $-\text{COO}^- - \text{Pd}^{2+}$ ion pairs in the Pd-salt MMA-MAA ionomer are due to the electrostatic interaction between $-\text{COO}^-$ and Pd^{2+} . The incompatibility of the $-\text{COO}^-$ pendant groups with the nonionic PMMA backbone chains would tend to result in clustering and the formation of Pd^{2+} -rich ionic aggregates. Additionally, Pd^0 nanoclusters would clearly be generated during the reduction reaction of the Pd^{2+} ions. If the mean size(s) is generally above 2 nm, then the $-\text{COO}^- - \text{Pd}^{2+}$ ionic aggregates and/or the Pd^0 nanoclusters containing the large atomic-number (*Z*) Pd element can be detected by the *Z*- and/or phase-contrast TEM technique, if they are present in the products, as dark nanodomains in bright-field images.

TEM images of the products from MMA-MAA and $\text{Pd}(\text{CH}_3\text{COO})_2$ reacted in a mixed solution of benzene/methanol (9/1 v/v) for 20 min, 4 h, 12 h, and 24 h were obtained (Fig. 1a-



Scheme 2 Poly(methyl methacrylate-*ran*-12.1 mol% methacrylic acid) (MMA-12.1% MAA) supported Pd^0 catalyzed the Heck reaction between iodobenzene and styrene to produce *trans*-stilbene.



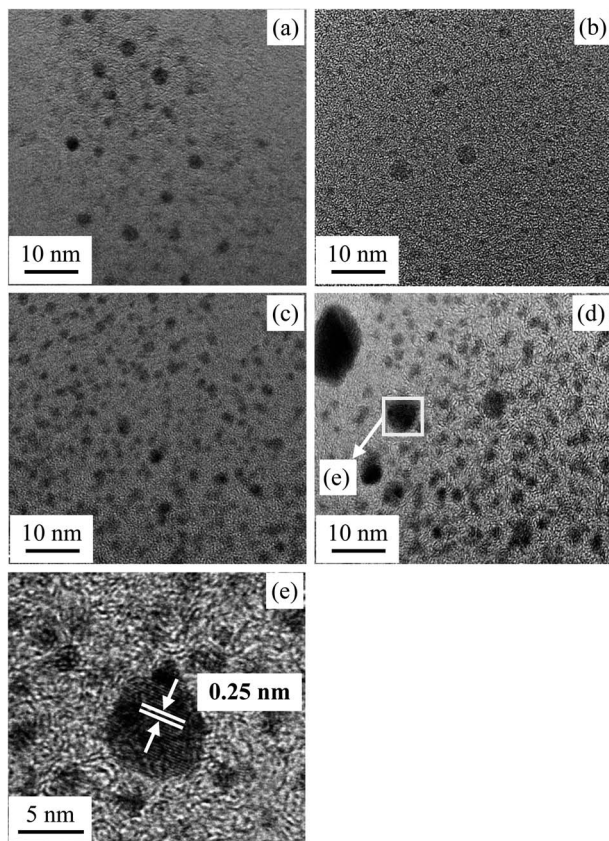


Fig. 1 Transmission Electron Microscopy (TEM) images of the products precipitated for reaction times of (a) 20 min, (b) 4 h, (c) 12 h, and (d) 24 h, all of which show nanodomains (*i.e.*, "dark spots"). Given in (e) is the "spot" chosen stochastically from (d) at a higher magnification; it is observed to contain electron diffraction patterns with a typical (minimum) interplanar spacing, d , of ~ 0.25 nm (2.5 Å), which is characteristic of the (111) crystallographic plane of face-centered cubic Pd⁰ crystallites; the same observation can be made for nearly all other "spots" in (a)–(d).

d respectively). Fig. 1 shows that spheroidal nanoparticles (*i.e.*, Pd²⁺-rich ionic aggregates and/or Pd⁰ nanoclusters) were formed as soon as the reaction was carried out for 20 min, similarly, when the reaction was extended from 4 to 24 h, spheroidal nanoparticles also formed. From the TEM images, it can be seen that the reaction was almost complete and the nanoparticles began to aggregate at 24 h. Further investigation under higher magnifications reveals that all the nanodomains (*i.e.*, "dark spots") in each of Fig. 1a–d were primarily (semi) crystalline Pd⁰ nanoclusters, despite the different ranges of internal periodicity (*i.e.*, sizes of crystallites). For example, the magnified image (Fig. 1e) of the "spot" randomly selected from the products reacted for 24 h (Fig. 1d) shows the obtained electron diffraction patterns. The calculated distinct interplanar spacing was ~ 0.25 nm (2.5 Å), which was consistent with the interplanar spacing (PDF #65-2867) of the (111) crystal plane of face-centered cubic (fcc) Pd⁰ crystallites. Similarly, almost all the other "spots" in Fig. 1a–b showed a similar d -spacing of ~ 2.5 Å at the appropriate magnification.

To further explore the change in size and size-distribution of the Pd⁰ nanoclusters with the extension of the solution reaction time, particle-size (*i.e.*, diameter) analysis was performed on the TEM micrographs (Fig. 1a–d), then the analysis results were correspondingly made into histograms (Fig. 2a–d) of the size distributions. The histograms of the Pd⁰-nanocluster diameter, d_0 , defined as an arithmetic mean of all the diameters in the corresponding TEM image, was evaluated by:

$$d_0 = \frac{\sum_i n_i d_i}{N}, \quad (1)$$

and the standard deviation, σ , around d_0 was estimated as:

$$\sigma = \sqrt{\frac{\sum_i (d_i - d_0)^2 n_i}{N}}, \quad (2)$$

in which d_i and n_i are the diameter and the number of the Pd⁰ nanoclusters, respectively, with the same arbitrary size, i , and N is the total number of Pd⁰ nanoclusters. As counted from the corresponding TEM micrograph, which is expressed by:

$$N = \sum_i n_i. \quad (3)$$

The results of d_0 and σ for the different reaction times were obtained and are summarized in Table 1, where the size (d_0) and size-distribution (σ) of the Pd⁰ nanoclusters can directly be observed and compared. As the reaction progressed from 20 min to 24 h, d_0 increased slightly, probably because of the slightly agglomerated nanoparticles, but it was basically stable at 2.5 ± 0.5 nm; all the σ values were relatively small, <1 , except for samples prepared for 4 h ($\sigma = 1.1$ nm). Smaller nanoparticles have a greater surface energy and it becomes more difficult to control the aggregation. However, the size of the Pd⁰ nanoclusters prepared by this method was basically unchanged and the size distribution was uniform. This may result from complexation between the Pd atoms on the surface of the Pd⁰ nanoclusters and the carboxyl oxygens of the polymer matrix in the dark at room temperature. Further, this also prevents the Pd⁰ nanoclusters from thermal aggregation at high temperatures; additionally, the polymer chain-segments adsorbed onto the surfaces of the Pd⁰ nanoclusters act as protection against agglomeration.

3.2 WAXS confirmation of Pd⁰ crystallite formation

To further confirm that the "dark spots" in the TEM images (Fig. 1a–d) were Pd⁰ nanoclusters rather than Pd²⁺-rich ionic aggregates, complementary WAXS experiments were conducted on all products (samples) retrieved at the different reaction times and their respective copolymer-acids (references), and the results are shown in Fig. 3. For each of Fig. 3a–d, curve 1 and 2 respectively represent WAXS patterns of the copolymer acid (*i.e.*, MMA–12.1% MAA) and the product. The multiple WAXS peaks, occurring at 2θ of $\sim 14^\circ$, $\sim 30^\circ$, and $\sim 42^\circ$ can be ascribed to "amorphous" peaks characteristic of diffuse scattering from small ordered domains of amorphous PMMA in both patterns.²⁶



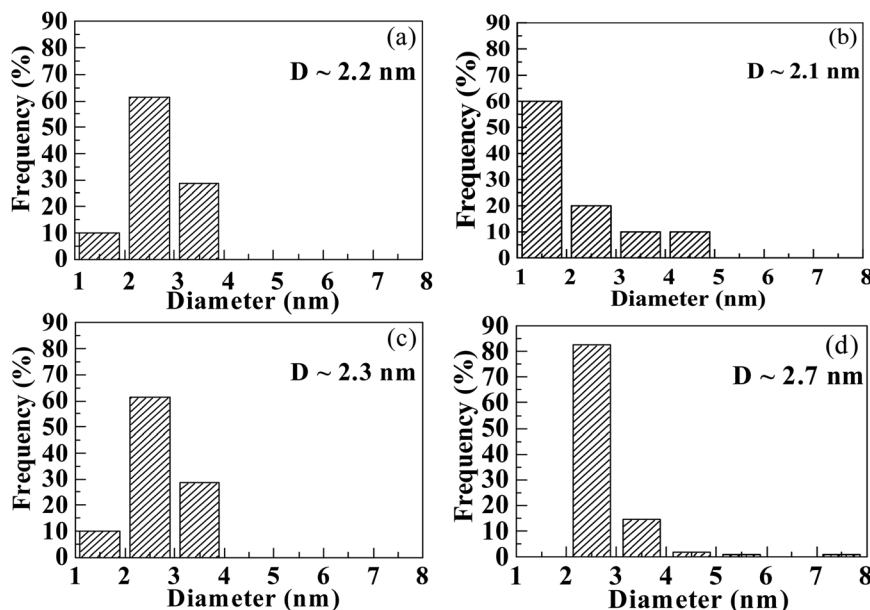


Fig. 2 Histograms of the size (diameter) distributions obtained from particle-size analysis of the TEM images (Fig. 1a–d), for the nanodomains (Pd⁰ nanoclusters) deposited inside the products that are precipitated upon solution reaction of a copolymer acid, poly(methyl methacrylate)-12.1 mol% methacrylic acid, with Pd(CH₃COO)₂ in a benzene/methanol mixed solvent in the dark at room temperature (~25 °C) for increasing durations: (a) 20 min, (b) 4 h, (c) 12 h, and (d) 24 h.

Table 1 Mean diameters, d_0 , and standard deviations, σ , about d_0 for the Pd⁰ nanoclusters within the polymeric products recovered at reaction times of (a) 20 min, (b) 4 h, (c) 12 h, and (d) 24 h

Product no.	Reaction time	d_0^a (nm)	σ^a (nm)
a	20 min	2.2	0.5
b	4 h	2.1	1.1
c	12 h	2.3	0.4
d	24 h	2.7	0.7

^a Both d_0 and the σ are evaluated from the Pd⁰-nanocluster size distribution histograms (Fig. 2a–d, respectively).

From Fig. 2, it can be seen that curves 1 and 2 are all almost parallel; hence, if there are crystallites in the nanodomains of the products, they should be so small that the relatively low-intensity Bragg signal is extremely weak. To conveniently observe whether there are crystallites in the nanodomains through the WAXS pattern, a weighted subtraction of the scattered X-ray intensities of the copolymer acid (reference) from those of each product (sample) was performed, according to:

$$I_3(2\theta) = I_2(2\theta) - fI_1(2\theta), \quad (4)$$

where $I_1(2\theta)$, $I_2(2\theta)$, and $I_3(2\theta)$ are the scattered X-ray intensities from the copolymer acid (reference), the product (sample), and the nanodomains at a given scattering angle of 2θ , respectively. The scale factor, f , was determined based on a trial-and-error method, where on subtraction, full suppression of the “amorphous” peaks of the copolymer-acid matrix and leveling-off of the declining baseline occurs. The average diameter(s), D , of the

crystallites, if spherical, in the nanodomains was estimated from the WAXS pattern of the nanodomains using the Scherrer equation:

$$D = \frac{0.9\lambda}{B \cos \theta_B}, \quad (5)$$

where λ is the wavelength of the X-ray (1.5418 Å), θ_B the half scattering angle of a major peak, and B the full width at half height (FWHM) of the major peak at $2\theta_B$. The WAXS signals of the nanodomains at different reaction times were obtained as shown in Fig. 3a–d as curve 3, with the f and the subtraction equation on the upper left corner of each curve 3.

It can be observed that within the studied 2θ range of 10–60°, the WAXS patterns of the nanodomains (curves 3) all have a peak at ~22.6–24.4° and ~37.2–39.9°. The peak at ~22.6–24.4° might likely derive from a subtraction mismatch, even upon an appropriate subtraction at a reasonable f , and thus, could not be considered as a Bragg-type reflection. This is because there is more than a pure physical interaction between the nanodomains and the MMA–MAA matrix (this will be discussed further in the next chapter). The other peak at ~37.2–39.9° was characteristic of the Bragg-type reflection from the (111) crystallographic plane of the fcc Pd⁰ crystallites,²⁷ which further proves that the nanodomains dispersed in the MMA–MAA matrix included Pd⁰ crystallites for all the products. The Pd⁰-crystallite reflections at ~37.2–39.9° based on WAXS coupled with the TEM results, show Pd⁰ crystallite d -spacings of 2.5 Å for almost all the investigated “spots”, which confirms that the nanodomains in the products were generally all Pd⁰ nanoclusters, regardless of the solution reaction time. The size (*i.e.*, diameter) of the Pd⁰ crystallites was calculated using the



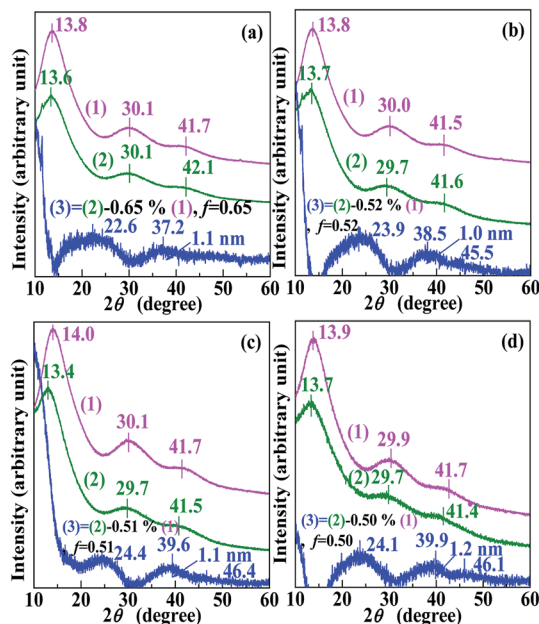


Fig. 3 Wide-angle X-ray scattering (WAXS) patterns of the nano-domains present in the retrieved products for reaction times of (a) 20 min, (b) 4 h, (c) 12 h, and (d) 24 h. They are resolved via weighted subtractions, from the WAXS signals of the products (samples), of the respective copolymer acids (references) with the same preparation histories. In each graph (a)–(d): curves 1, 2, and 3, respectively, are the WAXS patterns for the copolymer acid, the product, and the nano-domains deposited in the product; the value of the scale factor, f , as well as the subtraction equation used to resolve curve 3 are indicated over the curve; a peak appears at ~ 37.2 – 39.9° in curve 3, which characterizes the reflection from the (111) crystallographic plane of face-centered cubic Pd⁰-crystallites and thus confirms the presence of Pd⁰ crystallites in the nanodomains. The average diameter of the Pd⁰ crystallites estimated from the peak by the Scherrer equation is also indicated over curve 3 in graphs (a)–(d).

Scherrer equation (eqn (5)) and determined to be ~ 1.0 – 1.2 nm (indicated in the upper right corner of each pattern 3 in Fig. 3a–d), which was basically unchanged with varying reaction time. This is consistent with Fig. 1a–d, where over the entire 24 h of the solution reaction, the size (diameter) of the Pd⁰ nanoclusters remained almost constant (~ 2.5 nm) (*cf.* Fig. 1a–d, Fig. 2a–d, and Table 1). Therefore, the diameter of the Pd⁰ crystallites in the nanoclusters (*i.e.*, polycrystalline nanoparticles) correspondingly changed very little (~ 1.0 – 1.2 nm) (*cf.* Fig. 3a–d).

3.3 FT-IR spectroscopic analysis of products structures

FT-IR spectroscopic analysis was used to further analyze the structures of the products (Pd⁰/MMA-MAA). As shown in Fig. 4, in which Fig. 4a and Fig. 4b–e represents the FT-IR absorption spectra of purified MMA-MAA (reference) and the products obtained on the different reaction times, respectively. The absorption bands at 2953, 1732, 1460, and 1149 cm^{-1} were present in the reference and all the products in the MMA unit of MMA-MAA or the products, the C–H stretching of the methyl and methylene groups, the C=O stretching of the ester

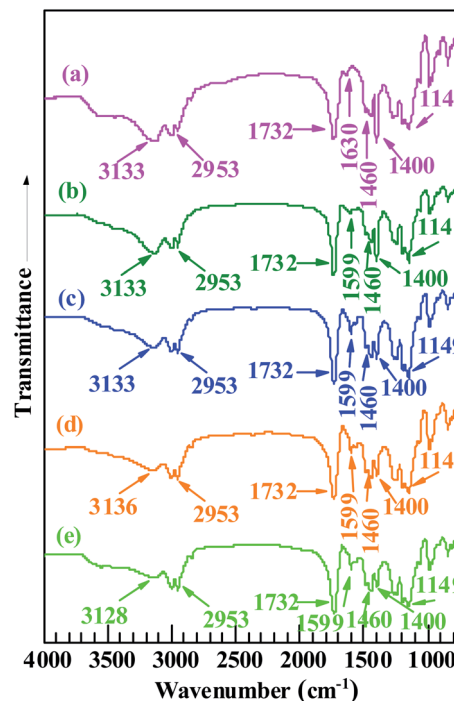


Fig. 4 Fourier transform infrared (FT-IR) absorption spectra of (a) a copolymer acid, poly(methyl methacrylate-*ran*-12.1 mol% methacrylic acid) (MMA-12.1% MAA), and (b–e) the products that are precipitated upon room temperature ($\sim 25^\circ\text{C}$), dark (light-free) solution reaction of the MMA-12.1% MAA with Pd(CH₃COO)₂ in a benzene/methanol mixed solvent for different durations: (b) 20 min; (c) 4 h; (d) 12 h; (e) 24 h.

carbonyl group, the C–H deformation of the methyl group(s), and the C–O–C stretching of the ester group, respectively. Their intensities all remained nearly constant with increasing reaction time. This is because the neutralization and/or reduction might only be associated with the MAA unit and/or the Pd(CH₃COO)₂.

In Fig. 4a, the absorption bands at 3133 and 1400 cm^{-1} were attributed to the stretching and in-plane bending of the O–H bonds in a dimer of carboxylic-acid groups formed *via* hydrogen bonding (*i.e.*, double coordination of either H atom to the O atoms from bridging bidentate carboxylate groups) within the copolymer acid, respectively. According to the results of previous TEM analyses (Fig. 1a–d) and WAXS (Fig. 3a–d), the reduced Pd⁰ nanoclusters were significantly present in the products retrieved after 20 min of the reaction. Additionally, Pd-carboxylate ionic aggregates formed by the neutralization reaction might also exist in the same product, but they were too small to be observed in the TEM images (Fig. 1a–d). There was coexistence of Pd⁰ and Pd-carboxylate for reaction times from 20 min to 24 h, hence, there could be four typical carboxylate complexes (Chart 1) in the products. These are: (1) the interactions of Pd⁰ nanoclusters with carboxyl groups, in which part of the surface Pd⁰ atoms are coordinated with the four O atoms of four asymmetric bridging-bidentate carboxylate groups, and a carboxylate of another O atom is complexed to an H atom (Chart 1a); (2) the Pd⁰-atom-carboxyl quadruplets (*i.e.*,



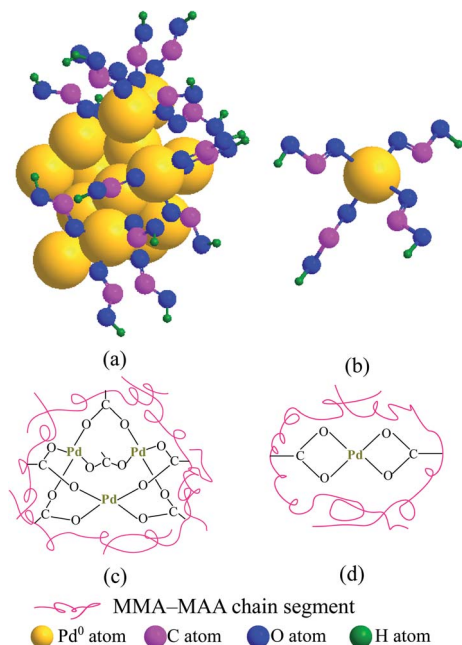


Chart 1 Illustration of the four typical carboxylato complexes structures possibly formed in the precipitated products for reactions with different durations between 20 min to 24 h: (a) a Pd⁰-nanocluster with some of the surface Pd⁰ atoms coordinated to the unsymmetrical bridging-bidentate carboxylate groups of the carboxyls; (b) a Pd⁰ atom complexed with the four noncoordinating O atoms of four carboxyls; (c) a $-2\text{COO}^- \text{Pd}^{2+}$ ionic aggregate with the Pd atoms coordinated to the symmetrical bridging-bidentate carboxylate groups; (d) a Pd atom coordinated to two bridging-bidentate carboxylate groups.

a singular form of Chart 1a) in which a Pd⁰ atom is coordinated with the four uncoordinated O atoms of four carboxyl groups (Chart 1b); (3) the Pd²⁺-rich ionic aggregates in which each Pd atom is four-fold coordinated to symmetrical bridging-bidentate carboxylate groups (Chart 1c); and (4) the isolated $-2\text{COO}^- \text{Pd}^{2+}$ ion pairs (*i.e.*, a singular form of Chart 1c) that comprise a Pd atom complexed to the four O atoms of a carboxylate group (Chart 1d).

It is well known that a pair of FT-IR absorption bands usually exist at frequencies (wavenumbers), ν , of 1765–1465 and 1490–1200 cm^{-1} that are characteristic of the antisymmetric and symmetric modes of the carboxylate C–O stretching of carboxylato complexes, respectively. Based on the coordination methods, there are mainly three types of carboxylate ligands, namely, unidentate, bridging bidentate, and chelating bidentate. Usually, unidentate ligands have a separation between the antisymmetric and symmetric frequencies, $\Delta\nu$, of $>200 \text{ cm}^{-1}$, while bridging bidentate and/or chelating bidentate ligands have a $\Delta\nu$ of 150–200 cm^{-1} (especially bridging bidentate, accompanied by a small amount for chelating bidentate). Returning to the FT-IR spectroscopic results in Fig. 4, it can be observed that the absorption bands at *ca.* 3133 and 1400 cm^{-1} that are characteristic of the dimeric carboxyl groups both weakened gradually from 20 min to 24 h of reaction time (Fig. 4a–d). One new peak emerged at 1599 cm^{-1} , which was assigned to the antisymmetric stretching of the bidentate-

carboxylate bridging; its corresponding symmetric stretch is likely obscured by the in-plane bending of the O–H bonds in the dimer of the carboxylic-acid groups at 1400 cm^{-1} . In this work, there were only bridging bidentate (Chart 1a–d) carboxylates in the system (with a $\Delta\nu$ of 199 cm^{-1}). The Pd atoms were either complexed with the noncoordinating oxygens of the carboxyls (Chart 1a and b) or might be coordinated to the oxygen of the H-deprived bridging carboxylates from the neutralization (Chart 1c and d, respectively). Both cases effectively reduce the concentration of free (*i.e.*, dimeric associative) carboxyl-group monomers present in the PMMA matrix. Given the reduction of both the FT-IR features of the dimerized carboxyls at reaction times above 20 min, it seems that the carboxyl dimers were susceptible to interference by the other carboxylato complexes (Chart 1) that consumed part of the free carboxyls. Any stochastic formation of the coordinated Pd⁰-nanoclusters (Chart 1a and b) and/or Pd²⁺-rich ionic aggregates (Chart 1c and d) might interrupt the residual free carboxyls randomly distributed along the PMMA chains; thus, decreasing their dimerization because of steric hindrance by the nanoclusters and/or aggregates. Therefore, compared with the copolymer acid (Fig. 4a), the generation of $-2\text{COO}^- \text{Pd}^{2+}$ and/or Pd⁰ caused a decrease in the carboxyl-dimer concentration at a reaction time of 20 min (Fig. 4b). Any significant formation of Pd⁰ clusters and/or the $-2\text{COO}^- \text{Pd}^{2+}$ aggregates further destroyed the dimeric structures of carboxyls on extension of the reaction beyond 20 min (Fig. 4c–e).

As discussed above, the 1599 and 1400 cm^{-1} peaks (in Fig. 4b–e) were attributed to the antisymmetric and symmetric stretching of the carboxylates from the Pd⁰-carboxyl coordination (Chart 1a and b), respectively, and/or the $-2\text{COO}^- \text{Pd}^{2+}$ aggregates (Chart 1c and d), *i.e.*, from the (coordinated) Pd⁰ nanoclusters or a combination of the Pd⁰ clusters and the Pd²⁺-rich aggregates. Formation of predominantly Pd²⁺-rich aggregates over the Pd⁰ clusters is not possible because significant Pd⁰ deposition occurred beyond 20 min of the reaction (Fig. 1a–d and 3a–d). It can be observed from Fig. 4b–e that no shift occurred in the peak positions that were initially at 1599 and 1400 cm^{-1} as the reaction progressed to 24 h. This indicated that in the case of simultaneous (significant) presence of the Pd⁰ clusters and the Pd²⁺-rich aggregates, their molar ratio would have remained constant regardless of the extent of the reaction. This was not likely to occur during the reaction and will be discussed further below in the next section.

3.4 Precluding of the possibility of Pd²⁺-rich-aggregate abundance *via* solubility tests coupled with FT-IR spectroscopy

The Pd²⁺-rich ionic aggregates, Pd⁰ nanoclusters, and carboxyl dimers are all basically composed of intermolecular cross-links with different strengths in the MMA-MAA matrix of the bulk products. For the $-2\text{COO}^- \text{Pd}^{2+}$ aggregates (Chart 1c), because Pd is a typical transition metal, the O–Pd bonds were more covalent than ionic-bare (*i.e.*, uncoordinated) Pd²⁺ ions on breaking of the O–Pd bond. This would be the case unless they had been reduced or otherwise coordinated *in situ*, which would



have led to them being very unstable (*i.e.*, highly oxidative). Furthermore, all the O atoms in the aggregate carboxylates participated in the cross-linking *via* coordination with the Pd atoms *via* symmetrical bridging. This resulted in strong, irreversible intermolecular cross-links that resist swelling and dissolution of the MMA-MAA chains during solvation. In contrast, for the Pd⁰-nanocluster-carboxyl coordination structures (Chart 1a), the covalent strength of the nonionic O-Pd bonds was weaker because bare (uncoordinated) Pd⁰ nanoclusters were chemically stable despite the tendency for aggregation on O-Pd bond breaking. Additionally, the O atoms of the carboxyls coordinating to the H atoms did not contribute to the cross-linking, making the cross-link density around the Pd⁰ nanoclusters generally lower than inside the Pd²⁺-rich aggregates. These Pd⁰ nanoclusters caused relatively weak, reversible intermolecular cross-links, which could easily transform to intramolecular ones upon solvation and realize dissolution of the MMA-MAA chains. The cross-linking of the MMA-MAA chains by the carboxyl dimers (not shown schematically), which were also intermolecular and reversible, were the weakest and they transformed readily into intramolecular bonds during dissolution. This is because of the poor chemical stability of the carboxyl monomers during O-H bond breaking, as well as the smallest aggregation number (2), and thus, the lowest cross-link strength of the carboxyl dimers.

Next, whether the products precipitated at reaction times between 20 min to 24 h could be re-dissolved in the benzene/methanol (9/1 v/v) mixed solvent was investigated. For this, a small amount (~30 mg) of each product was stirred with ~6.0 mL of the solvent in a 15 mL vial at room temperature to observe its solubility within ~2 h, and the results are summarized in Table 2. It can be noted from the table that the products at 20 min, 4 h, and 12 h of reaction were insoluble in the solvent. This shows that in terms of the cross-linking in the three products, the presence of Pd²⁺-rich aggregates was significant. There were also a large number of Pd⁰ nanoclusters in the three products. When the reaction was carried out for longer than 12 h, the products began to be soluble on approaching 24 h. This indicates that the concentration of Pd²⁺-rich aggregates in the system gradually decreased by a significant amount, which is likely because of their continuous reduction up to 24 h; at this point, the -2COO⁻-Pd²⁺ aggregates

almost disappeared and there only were the Pd⁰ nanoclusters in the product.

Therefore, if the Pd²⁺-rich aggregates were abundant in the products, significant changes in the composition of the nano-domains (*i.e.*, a mixture of the Pd⁰ nanoclusters and the Pd²⁺-rich aggregates) would have resulted across the reaction process from 20 min to 24 h. This was because the concentration of -2COO⁻-Pd²⁺ aggregates decreased and that of the Pd⁰ nanoclusters increased accordingly, which would cause appreciable shifts in the IR-absorption frequencies for both the antisymmetric and symmetric stretching of the carboxylate groups with reaction time. The reason for this is that the unsymmetrical bridging carboxylates in the Pd⁰-nanocluster-carboxyls coordination (Chart 1a and b) were different in character from the symmetrical-bridging in the -2COO⁻-Pd²⁺ aggregates (Chart 1c and d, respectively). However, the pair of bands that are characteristic of the carboxylate stretching remained unchanged in frequency with increasing reaction time from 20 min to 24 h, staying at 1599 and 1400 cm⁻¹ (Fig. 4b-e). At this point, we can rule out the assumption that there were abundant Pd²⁺-rich aggregates coexisting with the Pd⁰ nanoclusters in the products. It appears that the effects of small concentrations of ionic aggregates were insignificant to the IR absorption of the carboxylate, while it was significant for the irreversible cross-linking of the products. The solubilities of the products were much more sensitive to the rather small concentrations of Pd²⁺-rich aggregates (*i.e.*, irreversible cross-links) present, while the FT-IR spectra were unaffected. Here, the carboxylate stretching absorptions were primarily determined by the rich Pd⁰ nanoclusters coordinated to the MMA-MAA-matrix carboxyls (Chart 1a and b).

3.5 Precluding of the possibility of Pd(CH₃COO)₂ reduction and Pd-salt MMA-MAA ionomer self-redox reduction *via* contrast experiments

As shown in Table 3, the composition and color change (20 min *vs.* 24 h of mixing) of the solution-reaction mixture described in the Materials and methods section (mixture a) were compared with those of two other solutions (mixtures b and c) in the dark at room temperature. It can be seen from the table that from 20 min to 24 h of reaction in mixture a, the reaction system changed from maroon to black. This is because the Pd⁰ nanoparticles below 10 nm are black. Compared with mixture a, the reaction system turned brown after 24 h of reaction with mixture b. This is because methanol has a weak ability to reduce a small amount of Pd²⁺ to Pd⁰ in the reaction system. The solution color did not change after reaction with mixture c, indicating that acetone could not reduce Pd²⁺.

To investigate the role of the copolymer acid in the reducing reaction, a contrast experiment was conducted using mixture b, which had almost the same composition as mixture a, but without MMA-12.1% MAA, as shown in Table 3. It was observed that the maroon solution at the start gradually turned brown during the stirring process with mixture b up to 24 h. This revealed that little direct reduction of Pd(CH₃COO)₂ occurred in the dark at room temperature within the observation period of







Table 2 Solubilities in a benzene/methanol (9/1 v/v) mixed solvent at room temperature (~25 °C) within an observation time period of *ca.* 2 h for the products recovered at different reaction times (0 min, 20 min, 4 h, 12 h, and 24 h)

Product no.	Reaction time (min or h)	Solubility
a ^a	0 min	Soluble
b	20 min	Insoluble
c	4 h	Insoluble
d	12 h	Insoluble
e	24 h	Soluble

^a Product a is the (as-purified) MMA-12.1% MAA copolymer acid.



Table 3 Composition and color change (20 min vs. 24 h of mixing) of the solution reaction mixture used in this work for Pd⁰-nanocluster preparation (mixture a) compared with two other solution mixtures, mixtures b and mixtures c: all the solution mixtures are vigorously stirred in the dark at room temperature (~25 °C) for 24 h; compared with mixture a, there was no poly(methyl methacrylate-*ran*-12.1 mol% methacrylic acid) (MMA–12.1% MAA) in mixture b, while acetone was substituted for both the benzene/methanol (9/1 v/v) and the methanol in mixture c; the color of mixture a changed from maroon to black at 24 h of reaction, the color of mixture b changed from maroon to brown at 20 min to black at 24 h of the reaction, while the color of mixtures c remained maroon over the entire mixing process

Mixture no.	a	b	c
MMA–12.1% MAA (g)	0.6000	0	0.6000
Benzene/methanol ^a (9/1 v/v) (mL)	30	30	0
Acetone ^a (mL)	0	0	30
Pd(CH ₃ COO) ₂ (g)	0.0885	0.0885	0.0885
Methanol or acetone ^b (mL)	10 ^c	10 ^c	10 ^d
Color of mixture at 20 min	Maroon	Maroon	Maroon
Palette of mixture at 20 min			
Color of mixture at 24 h	Black	Brown	Maroon
Palette of mixture at 24 h			

^a For dissolution of MMA–12.1% MAA. ^b For dissolution of Pd(CH₃COO)₂. ^c Methanol. ^d Acetone.


24 h. Hence, the likely mechanism for the reduction of Pd²⁺ to Pd⁰ in a solution mixture of Pd(CH₃COO)₂ and MMA–12.1% MAA (mixture a) is neutralization of MMA–12.1% MAA with Pd(CH₃COO)₂ to produce the ionomeric Pd-carboxylate, which was subsequently reduced quickly to Pd⁰ nanoclusters. Hence, the concentration of the Pd-carboxylate in the system at any point was too small across the reaction durations to affect the carboxylate stretching IR-absorption frequencies (*cf.* Fig. 4) *via* its gradual decrease, as discussed above. The copolymer acid clearly served as an activator or a catalyst for the reduction of Pd(CH₃COO)₂ by formation of a highly reactive (*i.e.*, oxidative or reducible) Pd-carboxylate intermediate (*i.e.*, Pd-salt MMA–MAA ionomer) *via* neutralization. Without MMA–12.1% MAA, little Pd(CH₃COO)₂ could itself be reduced, presumably because of its relatively low activity in the dark at room temperature.

Hence, there is a question of whether the Pd-salt MMA–MAA ionomer was reduced by itself (self-redox) or by the solvent (electron transfer from the solvent) in mixture a. According to literature, the methanol in the mixed solvent, which has active α -H atoms, might have served as a reducing agent along with a smaller possibility of self-redox of the Pd-salt ionomer, even though neither heating nor photo-irradiation was applied in this work. To resolve this ambiguity, another contrast experiment was performed with mixture c in which acetone, without any active H atom, was substituted for both the benzene/methanol (9/1 v/v) and the methanol used in mixture a for the dissolution of MMA–12.1% MAA and Pd(CH₃COO)₂, respectively, with the other components (MMA–12.1% MAA and Pd(CH₃COO)₂) being the same as those in mixture a (*cf.* Table 3). It should be noted that like benzene/methanol (9/1 v/v) and methanol, acetone dissolves MMA–12.1% MAA and Pd(CH₃COO)₂ to form a solution, respectively. We again observed that a maroon color remained with little change throughout the 24 h stirring process of mixture c. This suggested that the formed Pd-salt MMA–MAA ionomer, if any, failed to be reduced to Pd⁰ in the absence of methanol in the dark at room temperature. From

this, it can be inferred that for mixture a, electron transfer from (the active H atoms of) the methanol rather than self-redox of the Pd-salt ionomer caused the reduction of the ionomeric Pd²⁺ to Pd⁰ nanoclusters.

3.6 Tentative mechanism for room-temperature dark solution-reduction of Pd²⁺ ions in the Pd(CH₃COO)₂/MMA–MAA/benzene/methanol system

Based on the above discussion, a tentative reduction mechanism in the dark at room temperature of Pd²⁺ ions in a benzene/

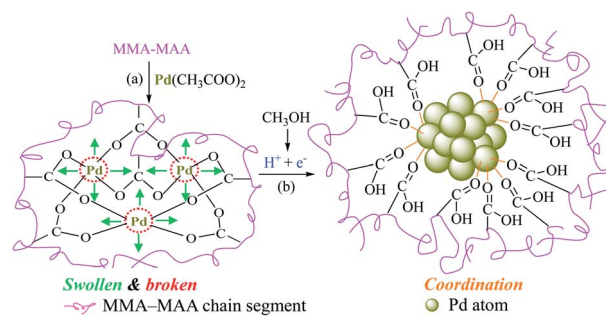

Scheme 3 Schematic representation of the tentative mechanism for the reduction of Pd²⁺ ions to Pd⁰ nanoclusters in a benzene/methanol solution of Pd(CH₃COO)₂/poly(methyl methacrylate-*ran*-methacrylic acid) (MMA–MAA) (dark, room-temperature): (a) the Pd(CH₃COO)₂ solution was added to the mixed solvent; solution neutralization of MMA–MAA with Pd(CH₃COO)₂ occurs to form the Pd-salt MMA–MAA ionomer with intramolecular –2COO⁻–Pd²⁺ ionic-aggregates. Then, the intramolecular aggregates (*i.e.*, cross-links) break up at the O–Pd coordination bonds upon intensive swelling of the chain-segments covalently connected to the aggregates *via* multiple C–C bonds to produce highly-oxidative, bare (*i.e.*, uncoordinated) Pd²⁺ ions as well as H⁺-associative –COO⁻ groups; (b) some of the methanol molecules are quickly oxidized to produce formaldehyde molecules, electrons, and protons, the Pd²⁺ and –COO⁻ ions, respectively, quickly scavenge the electrons and protons to produce Pd⁰ nanoclusters supported by re-formed MMA–MAA.²⁵




methanol (*i.e.*, methanol-containing) solution of $\text{Pd}(\text{CH}_3\text{COO})_2/\text{MMA-MAA}$ can be proposed, as schematically shown in Scheme 3. The $\text{Pd}(\text{CH}_3\text{COO})_2$ solution was added to the solvent system of benzene/methanol, followed by solution neutralization of MMA-MAA with $\text{Pd}(\text{CH}_3\text{COO})_2$ at a slow rate to form Pd-salt MMA-MAA ionomer with primarily intramolecular cross-links forming $-2\text{COO}^- - \text{Pd}^{2+}$ aggregates. On intensive swelling of the covalently attached MMA-MAA chain-segments,^{28,29} the O-Pd bonds break to give highly-oxidative, bare (*i.e.*, uncoordinated) Pd^{2+} ions as well as H^+ -associative $-\text{COO}^-$ ions (Scheme 3a). This excites some methanol molecules present in the solvent to oxidize quickly and form formaldehyde molecules, electrons, and protons (Scheme 3b), the latter two of which are scavenged rapidly by the Pd^{2+} and $-\text{COO}^-$ ions, respectively, to form Pd^0 nanoclusters coordinated to (*i.e.*, supported and protected by the carboxyls of) the re-formed MMA-MAA.²⁵

3.7 Catalytic property of $\text{Pd}^0/\text{MMA-MAA}$

To investigate the catalytic properties of $\text{Pd}^0/\text{MMA-MAA}$, it was used as catalyst for the Heck reaction between iodobenzene and styrene to generate *trans*-stilbene. It is well known that the catalytic property of a supported nanocatalyst is highly related to the content and size of the nanoparticles and the uniformity of its dispersion in the matrix.

Hence, the products ($\text{Pd}^0/\text{MMA-MAA}$) retrieved at reaction times of 20 min, 4 h, 12 h, and 24 h were analyzed. The products obtained at a reaction time for 20 min and 4 h had a lower degree of reaction, hence, the Pd^0 nanoclusters content was less, while the product obtained after a reaction time for 24 h had produced obvious aggregation (Fig. 1d and Table 1). Relatively, the product obtained after a 12 h reaction time had a higher degree of reaction and a more uniform dispersion (Fig. 1c), so it was selected for investigation of the catalytic properties. The catalytic mechanism is shown in Scheme 4: (a) the Pd^0 is oxidized and then added to iodobenzene to generate a C-Pd intermediate; (b) the C-Pd intermediate is reacted *via* (*cis*-)co-planar insertion with styrene to generate a Pd(II) intermediate; (c) the Pd(II) intermediate is (*cis*-)co-planar β -H eliminated to form *trans*-stilbene while releasing a hydrogen Pd(II) compound; (d) the hydrogen Pd(II) undergoes under a basic condition (self-)reductive elimination to revert to Pd^0 .

Fig. 5 shows the FT-IR absorption spectra of the reactants and products of the Heck reaction, in which the three curves represent (a) the as-purified styrene, (b) iodobenzene, and (c) the product (*trans*-stilbene). In Fig. 5a, the absorption bands at 3059, 1630, 1600, 990, and 773 cm^{-1} are the characteristic absorption peaks of styrene, which can be ascribed to the C-H stretching of aromatic ring, the C=C stretching of styrene, the skeleton of benzene ring, the C-H deformation of the ethylene bond in styrene, and the absorption peak of mono-substituted benzene ring, respectively. In Fig. 5b, the absorption bands at 3057, 1570, and 725 cm^{-1} can be attributed to the C-H stretching of the benzene ring, the skeleton of aromatic ring, and the absorption peak of mono-substituted benzene ring, respectively; these three vibrational absorption bands are characteristic absorption peaks of iodobenzene. In Fig. 5c, the

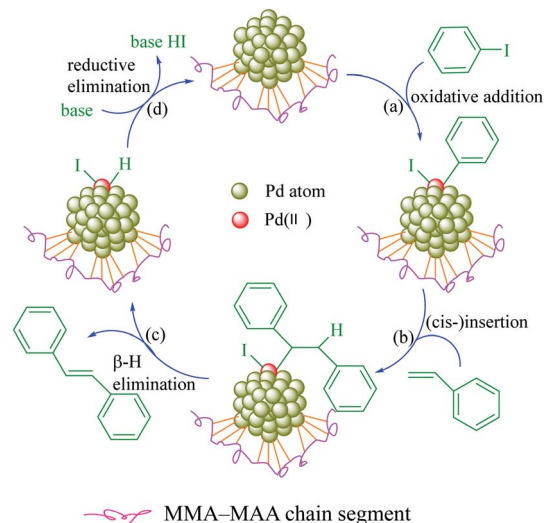

Scheme 4 Mechanism of the poly(methyl methacrylate-*ran*-12.1 mol% methacrylic acid) (MMA-12.1% MAA) supported Pd^0 catalyzed Heck reaction between iodobenzene and styrene: (a) the Pd^0 is oxidized and then added to iodobenzene to generate a C-Pd intermediate; (b) the C-Pd intermediate is reacted *via* (*cis*-)co-planar insertion with styrene to generate a Pd(II) intermediate; (c) the Pd(II) intermediate is (*cis*-)co-planar β -H eliminated to form *trans*-stilbene, while releasing a hydrogen Pd(II) compound; (d) the hydrogen Pd(II) undergoes under a basic condition (self-)reductive elimination to revert to Pd^0 .

absorption bands at 3057, 1596, 1446, 959, and 761 cm^{-1} can be ascribed to the C-H stretching of the aromatic ring, the stretching of the ethylene bond in *trans*-stilbene, and the absorption peak of the mono-substituted benzene ring, respectively, and the absorption bands at 1596 and 1446 cm^{-1} can be attributed to the skeleton of the aromatic ring. The results for the FT-IR absorption spectra show that the Heck reaction between iodobenzene and styrene was successfully carried out and the reaction product was *trans*-stilbene.

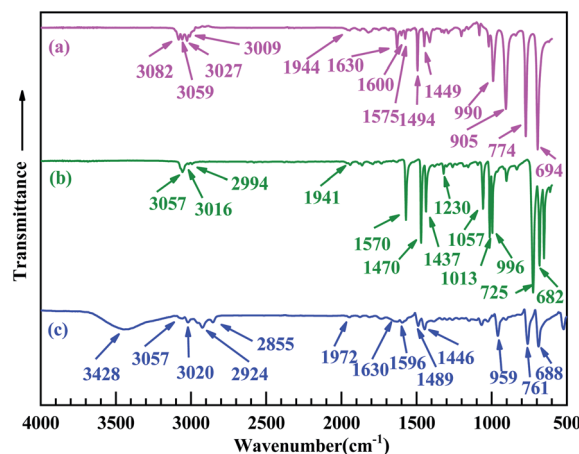


Fig. 5 Fourier transform infrared (FT-IR) absorption spectra of (a) (as-purified) styrene, (b) iodobenzene, and (c) styrene and iodobenzene undergoes the Heck reaction to form the *trans*-stilbene product.



Table 4 The reusability of the poly(methyl methacrylate-*ran*-12.1 mol% methacrylic acid) supported Pd⁰ (Pd⁰/MMA-MAA) nanocatalyst for the Heck reaction of iodobenzene with styrene^a

Run	Reaction time (h)	Yield ^b (%)
1	2	90.8
2	2	85.7
3	2	81.3

^a The reaction conditions: iodobenzene, 2.5 mmol; styrene, 0.3125 g; Pd⁰/MMA-MAA, 0.1049 g; Et₃N, 3.75 mmol; DMF, 2.5 mL; 100 °C.
^b Isolated yield.³⁰

As shown in Table 4, Pd⁰/MMA-MAA was reused three times to catalyze the Heck reaction between iodobenzene and styrene. The yield on first use was 90.8%, the second cycle yield was 85.7%, and the third reuse cycle had a yield of 81.3%. Because it is a heterogeneous catalyst, Pd⁰/MMA-MAA can be easily separated from the reaction system after each catalytic reaction. The traditional Pd/C catalyst reported in the literature,³¹ when catalyzing the Heck reaction between iodobenzene and styrene, the yield was 70% and the Pd/C catalyst was used only once. The results of the catalytic reaction showed that Pd⁰/MMA-MAA has more excellent catalytic properties and reusability than the Pd/C catalyst, it could be reused three times and the yields were all above 80%. As the number of repeated uses increased, the catalytic efficiency of Pd⁰/MMA-MAA gradually decreased, which was mainly due to the loss of Pd⁰ nanoparticles in Pd⁰/MMA-MAA.

4. Conclusions

In this work, using mechanochemical reduction as the driving force for the reaction, a poly(methyl methacrylate) supported Pd⁰ nanocatalyst was successfully prepared under very mild conditions (in the dark, room temperature, and without strong chemical reducing agent). A tentative mechanism was proposed: the Pd²⁺ ions in Pd(CH₃COO)₂ are exchanged, *via* their neutralization with the carboxyls of poly(methyl methacrylate-*ran*-methacrylic acid) (MMA-MAA), into a Pd-salt MMA-MAA ionomer; intramolecular -2COO⁻-Pd²⁺ ionic aggregation (*i.e.*, coordination cross-links) occurs in the solution, upon solvation (*i.e.*, swelling) of the ionomer chain-segments covalently bound *via* multiple C-C bonds. The O-Pd bonds are activated and ruptured by the resultant elastic forces to create transient bare (uncoordinated), highly-oxidative Pd²⁺ ions and H⁺-associative -COO⁻ ions. These ions rapidly scavenge the electrons and protons, respectively, of the active α -H atoms abstracted from the reductive methanol molecules of the mixed solvent to produce Pd⁰ nanoclusters (on aggregation of Pd⁰ atoms) supported by (*i.e.*, coordinated to the carboxyls of) the reformed MMA-MAA matrix.

The Pd⁰ nanoclusters prepared using this method of solution reduction in the dark at room temperature have a small particle size (diameter), and the average particle size of the Pd⁰ nanoclusters obtained after 24 h of reaction was 2.7 nm. At this

point, the Pd⁰ nanoclusters already had obvious aggregation. The average particle size of the Pd⁰ nanoclusters in the four samples obtained with reaction times of 20 min, 4 h, 12 h, and 24 h was stable at 2.5 ± 0.5 nm, and the corresponding crystallite size was maintained at 1.1 ± 0.1 nm. A part of the Pd⁰ atoms in the generated Pd⁰ nanoclusters form coordination bonds with the O atoms in the carboxyl group of MMA-MAA. This allowed the Pd⁰ nanoclusters to stably and uniformly disperse in the MMA-MAA matrix. The poly(methyl methacrylate-*ran*-methacrylic acid) supported Pd⁰ (Pd⁰/MMA-MAA) (obtained by reaction for 12 h) was selected to catalyze the Heck reaction of iodobenzene and styrene to produce *trans*-stilbene, it could be reused three times and the yield for the three reuse cycles was >80%. Compared with traditional Pd/C catalysts, the Pd⁰/MMA-MAA exhibited more excellent catalytic properties and reusability. As a heterogeneous catalyst, Pd⁰/MMA-MAA can be easily separated from the reaction system and reused in subsequent catalytic reactions. In addition, based on the excellent properties of Pd⁰/MMA-MAA in the Heck reaction between iodobenzene and styrene, we expect it to have similar outstanding potential in other cross coupling reactions.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We acknowledge with gratitude that this work was supported by the Open Fund of the Hubei Provincial Key Laboratory of Green Materials for Light Industry, China (contract no. [2013]2-key-3), as well as the Overseas High-level Talents Scientific-research Starting Fund of Hubei University of Technology, China (contract no. HBUT-science-[2005]2).

References

- J. Liu, F. He, E. Durham, D. Zhao and C. B. Roberts, *Langmuir*, 2008, **24**, 328–336.
- V. Polshettiwar and R. S. Varma, *Org. Biomol. Chem.*, 2008, **7**, 37–40.
- Y. Jiang, Y. Lu, F. Li, T. Wu, L. Niu and W. Chen, *Electrochem. Commun.*, 2012, **19**, 21–24.
- Z. Zou, Y. Jiang and K. Song, *Catal. Lett.*, 2020, **150**, 1277–1286.
- W. A. Herrmann, K. Öfele, D. V. Preysing and S. K. Schneider, *J. Organomet. Chem.*, 2003, **687**, 229–248.
- G. M. Neelgund and A. Oki, *Appl. Catal., A*, 2011, **399**, 154–160.
- R. F. Heck and J. P. Nolley, *J. Org. Chem.*, 1972, **37**, 2320–2322.
- N. Miyaura, K. Yamada and A. Suzuki, *Tetrahedron Lett.*, 1979, **20**, 3437–3440.
- N. Miyaura and A. Suzuki, *J. Chem. Soc., Chem. Commun.*, 1979, **19**, 866–867.
- D. Milstein and J. K. Stille, *J. Am. Chem. Soc.*, 1978, **100**, 3636–3638.



- 11 P. Serp, M. Corrias and P. Kalck, *Appl. Catal., A*, 2003, **253**, 337–358.
- 12 R. S. Varma, *Tetrahedron*, 2002, **58**, 1235–1255.
- 13 P. D. Stevens, G. Li, J. Fan, M. Yen and Y. Gao, *Chem. Commun.*, 2005, **21**, 4435–4437.
- 14 N. Yuan, V. Pascanu, Z. Huang, A. Valiente, N. Heidenreich, S. Leubner, A. K. Inge, J. Gaar, N. Stock, I. Persson, B. Martín-Matute and X. Zou, *J. Am. Chem. Soc.*, 2018, **140**, 8206–8217.
- 15 A. Nuri, N. Vucetic, J. H. Smått, Y. Mansoori, J. P. Mikkola and D. Y. Murzin, *Catal. Lett.*, 2019, **149**, 1941–1951.
- 16 S. Ghasemi and S. Karim, *Colloid Polym. Sci.*, 2018, **296**, 1323–1332.
- 17 Y. Nakao, *J. Colloid Interface Sci.*, 1995, **171**, 386–391.
- 18 C. Aymonier, D. Bortzmeyer, R. Thomann and R. Mülhaupt, *Chem. Mater.*, 2003, **15**, 4874–4878.
- 19 Y. N. C. Chan, G. S. W. Craig, R. R. Schrock and R. E. Cohen, *Chem. Mater.*, 1992, **4**, 885–894.
- 20 L. D. Rampino and F. F. Nord, *J. Am. Chem. Soc.*, 1941, **63**, 3268.
- 21 N. A. Dhas and A. Gedanken, *J. Mater. Chem.*, 1998, **8**, 445–450.
- 22 W. Tu and H. Liu, *Chem. Mater.*, 2000, **12**, 564–567.
- 23 X. Tong, Y. Zhao, T. Huang, H. Liu and K. K. Liew, *Appl. Surf. Sci.*, 2009, **255**, 9463–9468.
- 24 M. E. Gross, A. Appelbaum and P. K. Gallagher, *J. Appl. Phys.*, 1987, **61**, 1628–1632.
- 25 B. Li, T. Hu, N. Ma, Z. Hu, X. Gong, C. Wu and M. Hara, *Colloid Polym. Sci.*, 2017, **295**, 583–599.
- 26 N. M. Benetatos, P. A. Heiney and K. I. Winey, *Macromolecules*, 2006, **39**, 5174–5176.
- 27 Z. Yi, H. Xu, D. Hu and K. Yan, *J. Alloys Compd.*, 2019, **799**, 59–65.
- 28 S. Dursun, E. Yavuz and Z. Çetinkaya, *RSC Adv.*, 2019, **9**, 38538–38546.
- 29 M. S. Atas, S. Dursun, H. Akyildiz, M. Citir, C. T. Yavuz and M. S. Yavuz, *RSC Adv.*, 2017, **7**, 25969–25977.
- 30 D. Song and W. B. Yi, *J. Mol. Catal. A: Chem.*, 2008, **280**, 20–23.
- 31 X. Xie, J. Lu, B. Chen, J. Han, X. She and X. Pan, *Tetrahedron Lett.*, 2004, **45**, 809–811.

