

Cite this: *Chem. Sci.*, 2020, **11**, 9366

All publication charges for this article have been paid for by the Royal Society of Chemistry

Received 6th May 2020
Accepted 11th August 2020

DOI: 10.1039/d0sc02584d

rsc.li/chemical-science

The roles of chalcogenides in O₂ protection of H₂ase active sites

Xuemei Yang and Marcetta Y. Darensbourg *

At some point, all HER (Hydrogen Evolution Reaction) catalysts, important in sustainable H₂O splitting technology, will encounter O₂ and O₂-damage. The [NiFeSe]-H₂ases and some of the [NiFeS]-H₂ases, biocatalysts for reversible H₂ production from protons and electrons, are exemplars of oxygen tolerant HER catalysts in nature. In the hydrogenase active sites oxygen damage may be extensive (irreversible) as it is for the [FeFe]-H₂ase or moderate (reversible) for the [NiFe]-H₂ases. The affinity of oxygen for sulfur, in [NiFeS]-H₂ase, and selenium, in [NiFeSe]-H₂ase, yielding oxygenated chalcogens results in maintenance of the core NiFe unit, and myriad observable but inactive states, which can be reductively repaired. In contrast, the [FeFe]-H₂ase active site has less possibilities for chalcogen-oxygen uptake and a greater chance for O₂-attack on iron. Exposure to O₂ typically leads to irreversible damage. Despite the evidence of S/Se-oxygenation in the active sites of hydrogenases, there are limited reported synthetic models. This perspective will give an overview of the studies of O₂ reactions with the hydrogenases and biomimetics with focus on our recent studies that compare sulfur and selenium containing synthetic analogues of the [NiFe]-H₂ase active sites.

1. Introduction to hydrogenases

Much effort in enzyme isolation and purification in the past decades has permitted protein crystallographers to open the “black boxes” of the hydrogenase enzyme active sites exposing extraordinary organoiron fragments as components of remarkable hydrogen processing catalysts.^{1–6} Examples of the known classes, the nickel-iron hydrogenase, or [NiFe]-H₂ase, the diiron or [FeFe]-H₂ase, and the mono-iron or [Fe]-H₂ase, are shown in Fig. 1.^{1–5,7} While phylogenetically distinct, convergent evolution has found the benefits of the diatomic CO and CN ligands that are effective for π -delocalization and H-bonding, in the [FeFe]- and [NiFe]-H₂ase active sites. Both are presumed to have been natural targets for their ability to maintain low spin iron, while the CN additionally offers an H-bonding anchoring effect on the iron fragment into the protein pocket. Abundant sulfur is a key feature of the structures of the bimetallic subsites.^{1–5} With the [NiFe]-H₂ase active site this comes in the form of four cysteine connectors to the polypeptide chain. The [FeFe]-H₂ase has one cysteine that links the 2Fe subsite to a 4Fe4S, redox-buffering cluster as well as two additional sulfurs within a unique bridging azadithiolate. Thiolate sulfurs bridge the two metals in both [NiFe]- and [FeFe]-H₂ase and, due to orientation of intrinsic lone pairs, hold the two metals close in “butterfly” formation, of significance for M–M bonding as another tuning point for electron

delocalization as needed. Note that there are two subclasses of the [NiFe]-H₂ase; the major (>90%) is all sulfur-containing, while a minor contains one selenocysteine.^{2,3}

In addition to creating an appropriate electronic and structural environment in the ligand fields of the metals in the hydrogenase active sites, the myriad oxidation states possible for sulfur and selenium provide repositories for adventitious O₂. Reversibility in this chemistry is intertwined with abrogation of oxidative, irreversible damage at the metals. Thus, limiting the amount of reactive oxygen species is critical to the longevity of the biocatalyst.

The popularity of biomimetic research into hydrogenase active sites has been fostered by the possibility of proton reduction and hydrogen oxidation catalysis by abundant first row transition metals as molecular catalysts, as well as to further understanding of these remarkable biocatalysts.^{6,8} While synthetic ligand fields have yet to match the intricate and extended structures within the natural proteins, they are designed to approximate the electronic environment, and hopefully the function, of core features of those sites.⁹ For simplicity of interpretation, most electrocatalytic studies of model complexes for proton reduction to H₂ have been carried out in the absence of O₂. However, studies of the oxygen-damaged active sites, particularly the Ni-A and Ni-B states for the [NiFe]-H₂ase, were seminal to the development of this field long before the precise interpretation of the various active site structures in their reduced forms was possible.^{6,9–11} Since that time, protein XRD has generated many structures of “oxygen-damaged” hydrogenase active sites of [NiFe]-H₂ase. Our

Texas A&M University, Department of Chemistry, College Station, TX 77843, USA.
E-mail: marcetta@chem.tamu.edu



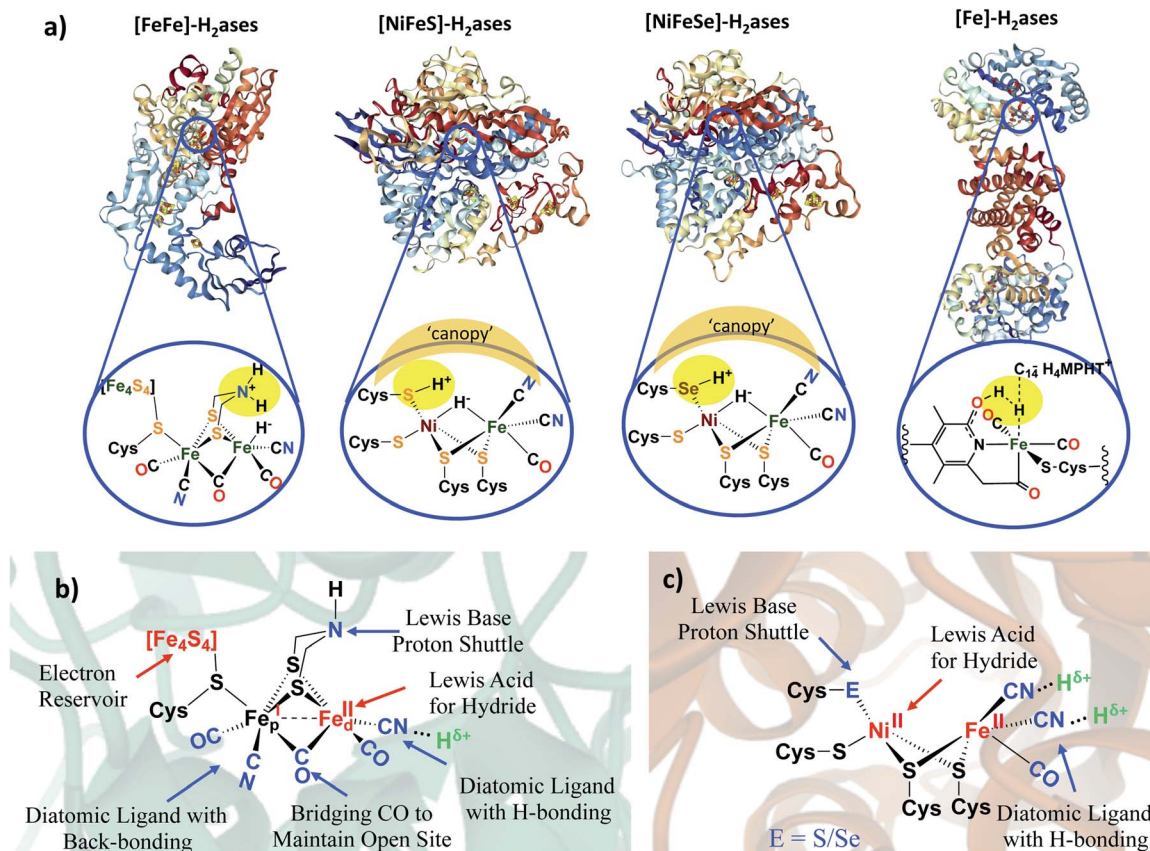


Fig. 1 (a) Selected structures of hydrogenase proteins exemplary of the four known classes, with blow-ups of their active sites.^{1–5} Hydrogen atoms in expected (or actually detected in the case of the Ni–R form of [NiFeS]–H₂ase),⁵ idealized positions for proton–hydride coupling (or the reverse, heterolytic H₂ splitting) via pendant base proton shuttles within the first coordination sphere; a “canopy” of critical immediate outer coordination sphere residues indicated by shaded area;⁷ (b) functional analysis of [FeFe]–H₂ase active site components in second coordination spheres; (c) functional analysis of [NiFe]–H₂ase active site components.

Perspective is largely limited to reports of oxygenated biomimetics of these sites. Numerous excellent reviews of the hydrogenases and models of their active sites are available such that our description of the features that control their interactions with protons or dihydrogen will be only for comparison to the more excellent electrophile, O₂. The mono-iron H₂ase is neglected here as its well known air sensitivity has, at this time, not been explored.

2. Strategies used by O₂-tolerant [NiFeS]– and [NiFeSe]–H₂ases


2.1 Deeply buried active sites and hydrophobic/hydrophilic access channels

Microorganisms that require the H₂ase enzymes, likely representing Earth's earliest life forms, developed strategies to protect their exquisitely evolved, hydrogen-processing catalysts with respect to the poisonous O₂ toxin as it built up in the atmosphere on the planet. An obvious strategy for the host organism is to confine itself into protective surroundings. Much like synthetic organometallic chemists that perform air-sensitive reactions in glove boxes filled with inert gas, or in special glassware on vacuum lines, many organisms that

require hydrogenases operate in the low oxygen, reductive conditions at the bottom of ponds and rivers. In addition, on the molecular level within the organism, the active sites of the hydrogenase enzymes are buried deeply within the folds of their host proteins.⁶ Strings of iron–sulfur clusters guide electrons into and out of the active sites of the [NiFe]– and [FeFe]–H₂ases. Hydrophobic and hydrophilic channels further control access or exit of H₂ and H⁺, respectively, apparently terminating at the ideal position of reactivity.¹² The hydrophobic channel(s) also provide a path for O₂ access. Attesting to the validity of this conclusion are mutagenesis studies that show a dependence on oxygen damage at the active site of [NiFe]–H₂ase from the *Ralstonia eutropha* organism with modification of specific amino acid residues that control the size of the channel.¹²

A recent (2019) study involving the [NiFeSe]–H₂ase from *D. vulgaris* Hildenborough challenges the conventional wisdom that hydrophobicity is considered optimal for diffusion of neutral diatomics, H₂ as substrate, or O₂ or CO as inhibitors.¹³ Pereira, Matias, Leger, *et al.* found that a hydrophilic channel modified by mutation of two glycine residues with alanine or serine resulted in more O₂-tolerant variants, without changing the hydrogenase activity. Such mutations, expected to narrow this channel, prevented or slowed the oxidation of the active-



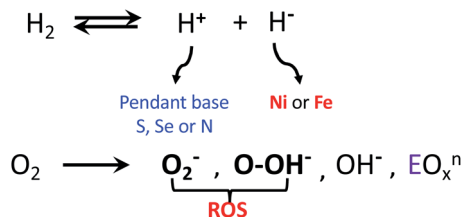

Scheme 1 H_2 and O_2 reactions in hydrogenase enzymes; O_2^- and OOH^- are designated as reactive oxygen species (ROS).⁶

ultimate degradation of the low valent iron to inactive oxo-species. While the reductive cost of four electrons is great, rapid conversion of the bound O_2 to hydroxide anion, followed by protonation yielding water, is the ultimate answer to safe O_2 removal from the active sites.^{16–18}

A fascinating chemical line of defense using a rapid conversion approach has been identified for the [NiFeS]- H_2 ase in the membrane-bound hydrogenase (MBH) from *Ralstonia eutropha*.¹⁶ While the core NiFe component is identical in [NiFeS]- H_2 ase's from various sources, and the electron transport iron sulfur chain operates similarly, there is an impressive compositional and structural modification in the iron sulfur cluster that is proximal to the NiFe site. Identified by X-ray crystallography by Friedrich, Lenz, *et al.*, and by Higuchi, *et al.*, as a [4Fe3S]6Cys cluster, one structural sulfide is displaced from a normal 4Fe4S cluster, generating a [4Fe3SS'] "cubane", where the S' is a cysteinyl sulfur from the CysCys motif and is bridging two irons, Fig. 3.^{16–18} The sixth cysteine is on another iron, balancing the oxidation states within the cluster. When called upon by polarization at the NiFe site as O_2 invades, the CysCys dipeptide assists the 4Fe3S cluster in providing electrons to the O_2 electrophile by stabilizing the

resulting superoxidized cluster, Fig. 3. This stabilization is a result of the deprotonation of the amide nitrogen and its minor shift into bonding range of the iron. The reversibility of this concomitant structural/redox change is key to the oxygen tolerance of MBH, which actually operates in the presence of O_2 .^{16–18}

2.4 Metal-protection by chalcogens

Another strategy for O_2 evasion and repair of oxidation, particularly seen for the NiFe hydrogenases, is the oxygenation of the chalcogens. Found in the crystals of [NiFeS]- H_2 ase as early as 1995, the sulfoxygenates were eventually and convincingly associated with EPR signals attributed to Ni(III) (Ni-A and Ni-B states) that correlated with reactivity recovery.^{19,20} Selected samples of these crystalline-trapped Ni and S-oxygenates are shown in Scheme 2.^{21–24} The Ni-Fe derivatives bridged by hydroxide, representing the easiest to be reduced and returned to full activity, are still referred to as Ni-B, Fig. 2 and Scheme 2. The slow-to-recover sulfoxide species are known as Ni-A.

Note that all the oxidized/oxygenated NiFeS species contain EPR-active Ni(III); at least 20 different examples are known from gaseous O_2 -infused crystallization approaches. Although fewer examples have been identified, the analogous [NiFeSe]- H_2 ase find a richer variety of oxidation or oxygenation.^{23,24} None of the latter contain Ni(III) but rather chalcogenate oxidation to S-S and Se-S bonds is seen as well as the 2-oxy species in the form of sulfates and selenates. The latter, complex e in Scheme 2, is uncommon if not unknown in chalcogen chemistry, and likely only chemically available in the confines of the metallo-enzyme active site pocket where Se-O-Ni interactions likely stabilize the selenate. While the Ni-A and Ni-B are proposed to be reactivated by adding electrons and protons with "O" removal as H_2O , the association of the [NiFeSe]- H_2 ases with sulfate-


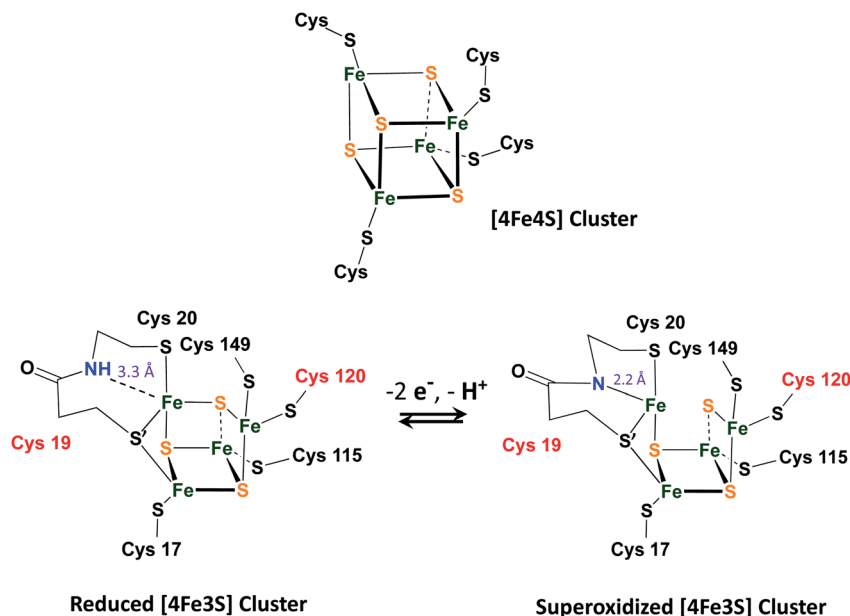


Fig. 3 A typical [4Fe4S]4Cys cubane cluster (top) and (below) the exceptional, [4Fe3S]6Cys cluster that is proximal to the [NiFeS]- H_2 ase active site.^{16–18}



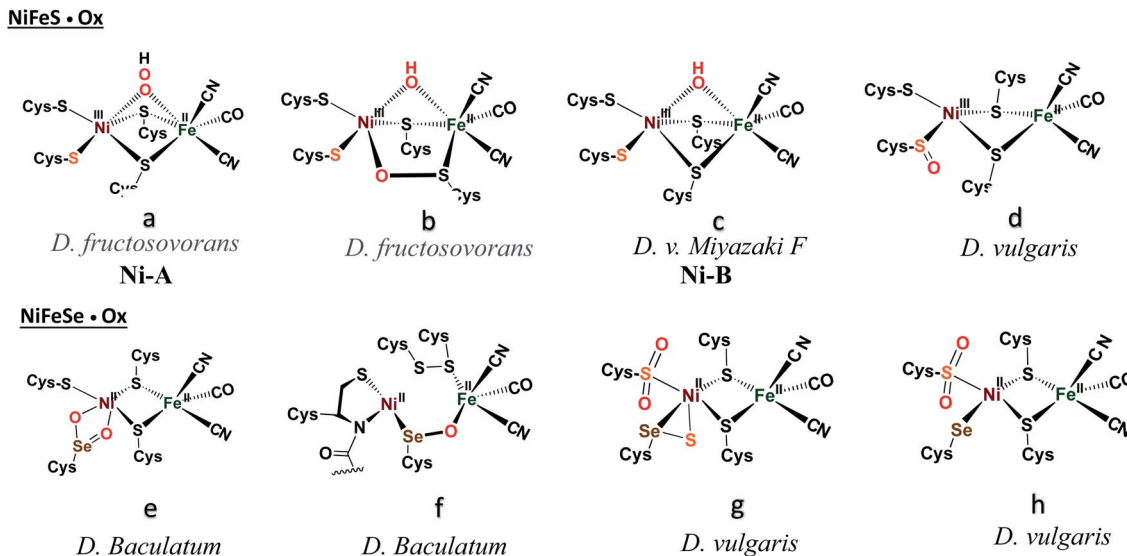

Scheme 2 A selection of structurally characterized oxygenates of [NiFeS]- and [NiFeSe]-H₂ase active sites.^{21–24}

reducing bacteria suggests another hypothetical repair mechanism: H₂S derived from sulfate assists Se–O or S–O reduction in oxygenated [NiFeSe]-H₂ases.^{25,26} This hypothesis is supported by the identification of H₂S in the [NiFeSe] enzyme's crystal structure (~7 Å away from active site), as well as the oxidized Se–S bound in the oxidized structure.²⁴

3. Synthetic models for O-damaged [NiFe]-H₂ases

3.1 Sulfoxylation in nickel complexes

Sulfoxylation of metal-bound thiolates, in synthetic compounds and in biological active sites, is actually quite common. There is a post-translational modification that generates S-oxygenates in the nitrile- and thiocyanate-hydratases containing non-heme iron or cobalt within in an N₂S₂ ligand field derived from Cys–Ser–Cys tripeptide motifs.^{27,28} The protein crystal structures of NHase's display the organization made possible through H-bonding of water to the oxygens of terminal sulfinate and sulfenate which optimally positions the substrates for hydration of the metal-bonded nitrile or thiocyanate.

Fig. 4, panel (a), presents a selection of sulfinate and sulfenates from controlled oxygenation of a series of NiN₂S₂ explored in our laboratories in the 1990's.^{29–32} We stress that examples of S-oxygenation are not confined to the thiolate-modified diazacycles. A number of examples have been reported in detail from the Maroney laboratory especially.^{33–35} Nevertheless, as mentioned above, the Cys–X–Cys biomimetic N₂S₂ tetradentate ligands with contiguous S–N–N–S donor sites represent particularly a convenient platform for such reactivity studies. The rigidity of the tetradentate N₂S₂ ligand doubtless contributes to the thermodynamic stability that was foundational for later studies of oxygen-damaged hydrogenase enzyme active sites. The value of this platform is to tip the balance of S-

based reactivity from electron transfer leading to dissociated disulfides to O-atom uptake or S-oxygenation maintaining the Ni–Fe core structure. In the confines of the protein matrix, both processes are seen in the oxygen-damaged [NiFe]H₂ase active sites, with all representing unwanted states. In the nitrile hydratases, the S-oxygenates serve a purpose.

Oxygen reactivity at sulfur was also discovered in monomeric nickel complexes developed from cleavage of [NS₂Ni]₂ and [NSE₂Ni]₂ complexes by cyanide.³⁵ Sulfinato (2-oxy) species resulted on addition of O₂ to the [NS₂Ni(CN)][–] anion, however the analogous selenium analogue was said to be stable to oxygen for up to 4 days. Sulfoxylation occurs on a single S, and isotopic labeling suggests the oxygen uptake from O₂ occurs by a concerted mechanism.³³ This study provides a rare opportunity to explore the chemical differences of S vs. Se when bound to nickel.³⁵

As indicated in panel (a) of Fig. 4, the rich nucleophilic chemistry at the non-oxygenated, reduced nickel-dithiolate includes the ability to serve as metallodithiolate ligands to a variety of Lewis acid, transition metal receivers, notably, iron.^{36,37} From such reactions the Ni(μ-SR)₂Fe butterfly core of the [NiFe]-H₂ase active site was obtained; some examples of these demonstrated electrocatalytic ability in the proton reduction, Hydrogen Evolution Reaction (HER).

3.2 O-damaged Ni–Fe heterobimetallics bridged by sulfurs

Panel (b) in Fig. 4 displays features of H₂ uptake by one of hydrogenase biomimetics as well as an O₂ binding study at iron.^{38–42} The former, with hydride located between Ni and Fe is an approximate model of the Ni-R state (Fig. 4b) of the [NiFe]-H₂ase which has been shown by crystallography to contain H₂ in “arrested” heterolytic cleavage.⁵ The latter is the first reported example of a side-on Fe^{IV} peroxy complex, which is a biomimetic for a postulated oxygen-bound species in [NiFe]-H₂ase.³⁸ It is derived from bubbling O₂ gas into a propionitrile solution



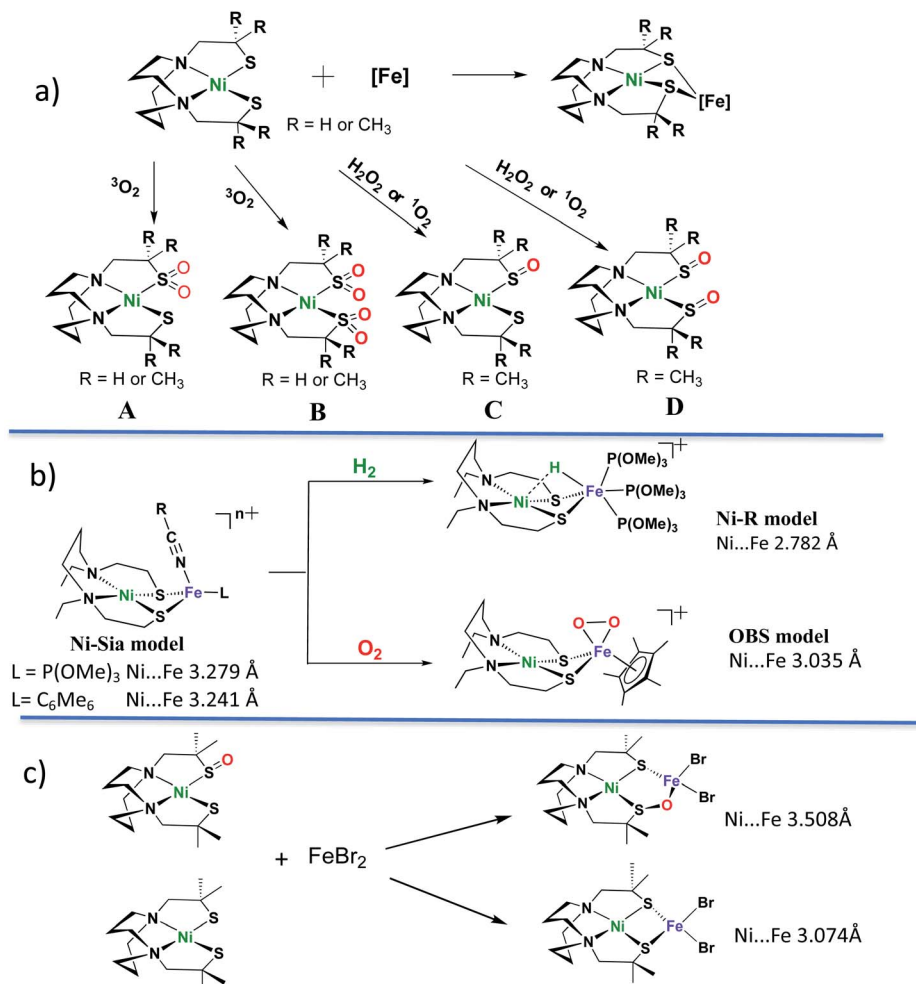


Fig. 4 Sulfoxygenates from monomeric NiN₂S₂ and examples of NiN₂S₂ in NiFe complexes. Descriptions of (a)–(c) are in text.^{29–32,36–43}

at $-80\text{ }^{\circ}\text{C}$ or acetonitrile at $-40\text{ }^{\circ}\text{C}$ in its reduced form (the Ni-Sia model in the Fig. 4b) with a 30% yield.³⁸ The oxygen uptake shortens the Ni...Fe distance as compared to the reduced form by *ca.* 0.2 Å (3.2325(6) Å in reduced and 3.0354(7) Å in the oxidized form). The iron peroxide species can be returned to the reduced form by supplying an electron source, ⁿBu₄NBH₄, and EtOH as proton source.³⁸

No sulfur oxidation was reported in the Ogo *et al.* studies of NiN₂S₂·(η⁵-C₅H₅)Fe complexes. In fact, to our knowledge no S-oxygenation of any Ni(μ-SR)₂Fe complexes in which the dithiolates are connected into the tetradentate N₂S₂ ligand has been thus far observed. The chelated backbone in the ligand and sulfur bridging between metals likely evades O₂ attack on sulfur; instead, the labile solvent binding on iron provided a reaction site for O₂.³⁸

Panel (c) of Fig. 4 summarizes a report from Driess and coworkers where structures derived from reaction of NiN₂S₂ and NiN₂S(SO), *i.e.*, the reduced and the isolated nickel monosulfoxygenate from Panel (a), with FeBr₂, were compared.⁴³ This first model complex of an oxygen-damaged [NiFe]-H₂ase active site was assembled from pre-formed components, and its structure shows a ~ 0.4 Å expansion of the NiFe core from that

of the reduced form. That is, the distance between Ni and Fe (3.508 Å) within the 5-membered NiSOFeS ring contrasts to the 4-membered NiSFeS “reduced form” (3.074 Å), and, differing from the Ogo study, there are no oxidation state changes on the metals. Although further explorations on conversions between the two forms were not reported, this study suggested an approach to model complexes for sulfur-oxygenation and O-damaged [NiFe]-H₂ase.

3.3 O-uptake in complexes related to [NiFeS]- and [NiFeSe]-H₂ases active sites

The pursuit of [NiFe]-H₂ase synthetic analogues designed to contrast the Cys-S and Cys-Se analogues would appear to be a valuable endeavor. While the biological and electrochemical/biological studies that query these differences are rather mature, there are few reports of model compounds that might be used for this purpose. Nature’s design for the [FeFe]-H₂ase is clear regarding the role of a pendant base for the final steps of proton transfer into reduced iron, to generate an iron hydride.⁶ The [FeFe]-H₂ase pendant base is a secondary amine nitrogen positioned just over an open site on the reactive iron—the site destined to become Fe-H or Fe-(η²-H₂) with added electrons



and a proton or with capture of H_2 , respectively.⁶ The well-engineered open site on the distal iron, needed for proton uptake or H_2 bonding in the productive chemistry, also accounts for the greater air-sensitivity of the $[FeFe]-H_2ase$.

The Ni-R state of $[NiFeS]-H_2ase$, Fig. 2, indicates a terminal thiolate S performs the role of base in the $[NiFe]-H_2ase$ mechanism.⁵ Hence it is not surprising, in view of the superior properties of $[NiFeSe]-H_2ases$ that the analogous position, the terminal cysteine that plays a critical role as “pendant” base in the final steps of H^+ delivery to the NiFe assembly or alternately in the opposite direction holds the proton in Ni-R, is precisely where SeCysteine resides.^{2,3} The superior properties of $[NiFeSe]-$ over $[NiFeS]-H_2ases$ include better HER catalytic ability, reduced H_2 inhibition and rapid reactivation from O_2 damage.⁴⁴ Protein film voltammetry studies of the $[NiFeSe]-$ hydrogenase by Armstrong *et al.* have found that the enzyme retains partial catalytic activity for H_2 production even in the presence of 1% O_2 in the atmosphere.⁴⁵ We point out that the immediate outersphere “canopy” described earlier provides a nearby base that might perform this function, however further distanced from the eventual proton lodging site than the terminal cysteinyl S or Se.⁷

The key experiments that demonstrated the lower catalytic activity and higher oxygen sensitivity (poorer tolerance) of $[NiFeS]-$, as compared to $[NiFeSe]-H_2ase$, derived from the single site mutagenesis of Se-cysteine to cysteine from identical bacterial sources, the enzyme in *D. vulgaris* Hildenborough.¹⁴ If the reasons for these superior properties of $[NiFeSe]-H_2ase$ lie solely with the elemental differences in chalcogens (rather than some as yet not established subtle differences in protein residues or folding), there are obvious explanations. The larger size of Se, with more electrons and higher polarizability results in better nucleophilicity of the RSe^- , higher acidity, of $RSeH$, and lower redox potential than sulfur.²⁶ Higher acidity is proposed to be the reason for better “ H^+ ” shuttling and higher H_2 production of $[NiFeSe]-H_2ases$.⁴⁴ Concomitantly, the larger size means that Se-O bonds, once formed because of the better nucleophilicity, are weaker than S-O. Thus facile Se-O bond release accounts for high oxygen-tolerance of $[NiFeSe]-H_2ases$.^{14,26,44}

The synthesis of appropriate synthetic analogues of enzyme active sites requires precursors that contain similar core features and sufficient stability to be chemically assayed in some way that relates to the reactivity of the enzyme function. Such concomitant requirements are not always easily met as the protein matrix stabilizes structures that are slightly distorted from the thermodynamic first-coordination sphere choices of ligand and metal that are seen in the “free world” of solution/molecular chemistry. Lubitz and coworkers generated a complex ligand system as an apt model of the sulfur-rich nickel subsite in $[NiFe]-H_2ase$, and one that could be modified to include selenium, Fig. 5.^{46,47} Importantly, these models have a terminal chalcogenide, which could be viewed as a pendant base for proton shuttling to reduced iron. With $E = S$, the NiFe complex is capable of electrochemical catalysis of H_2 production in aprotic solvents; however, in the selenium analogue, which was explored by Reisner, *et al.*, electrocatalytic

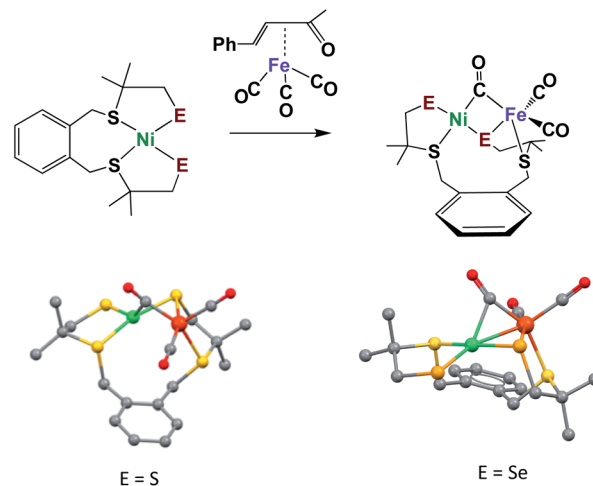


Fig. 5 Model complexes for $[NiFe]-H_2ase$ active sites with terminal S or Se.^{46,47}

H_2 production derives from species that deposit on the electrode.⁴⁷ Studies of these compounds were carried out under air-free conditions, and, to our knowledge, they have not been explored for oxygen uptake.

A somewhat related dinickel complex, $[NE_2Ni]_2$, with bridging and terminal thiolates, was the synthetic precursor to the $NS_2Ni(CN)$ complex described above. Reactions with O_2 finds uptake at the terminal thiolate S for the $[NS_2Ni]_2$ yielding the terminal sulfinate $[N(\mu-S)SO_2Ni]_2$. However no such reaction was observed with the analogous $[NSE_2Ni]_2$ complex having selenium as terminal chalcogen.⁴⁸

With the goal of pursuing heterobimetallics, and heterochalcogenates, for their potential as more stable electrocatalysts, we have adopted dimeric $[N_2SNi]_2^{2+}$ as synthon, Fig. 6. The simple dinickel butterfly complex precursor may be split by various nucleophiles including carbenes, imidazoles, thiolates, and selenoates.^{49–51} With the chalcogenates, entry to NiFe bimetallics is possible making use of the $(\eta^5-C_5H_5)Fe(CO)(NCCH_3)_2^+$ receiver species outlined in Fig. 6. Although less sophisticated than the Lubitz/Reisner models, and lacking the EAS requirement for a terminal chalcogenide as pendant base, the products from the $^-SC_6H_4X$ and $^-SeC_6H_4X$ nucleophiles are nevertheless informative. Specifically, it is possible to correlate the response of irreversible E_c reduction potentials for both the monomeric $NiN_2S(SAr)$ and the derivative $[NiFe]-$ heterobimetallics, as well as $\nu(CO)IR$ values for the latter, according to the remote effects of X in the $^-EC_6H_4X$ *via* Hammett parameters. The shifts in the $\nu(CO)$ positions are small, yet they systematically vary within the series with electron-donor ability of X, indicating the polarization of electron richness from the S or Se to Fe is further transmitted *via* π -backbonding to CO. From $\nu(CO)$ values it is also concluded, as expected, that the aryl selenoates are more donating to iron than the analogous aryl thiolates. In fact, a type of synthetic alchemy is seen to convert S into Se in terms of the equivalence of the electron-donating ability of $p^-SC_6H_4NH_2$ and $^-SeC_6H_5$.⁵⁰




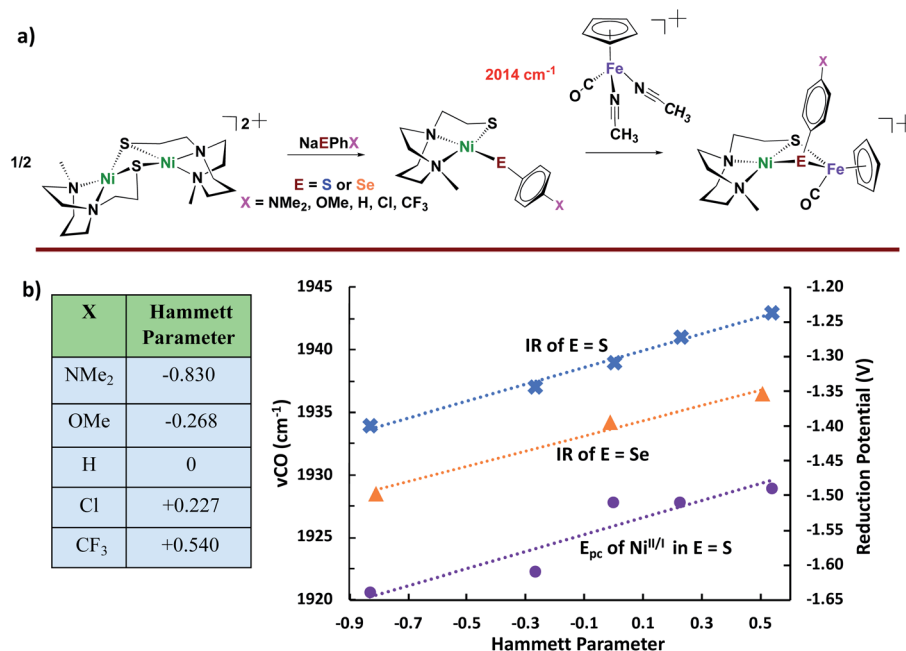


Fig. 6 (a) Synthetic approach for Ni₂ dimer-splitting leading to NiFe bimetallic analogues of [NiFeS]– and [NiFeSe]–H₂ase active sites; and (b) correlation of redox potentials and $\nu(\text{CO})$ IR data with Hammett parameters.^{49–51}

Included in the detailed characterization of the new complexes, is their reactivity with O₂, Scheme 3. Unlike the tetradentate NiN₂S₂ monomeric complexes which form oxygenated sulfur species, exposure of the Ni(N₂S)(EPh) to O₂ results in degradation. Nevertheless, as metallo-dichalcogenide ligands in NiFe complexes, O₂ uptake occurs at the monodentate bridging chalcogenide, leading to the conversion of the butterfly bimetallic, Ni(μ-EPh)(μ-S_{N2})Fe (E = S or Se), to a stable Ni–O–EPh–Fe–S_{N2} 5-membered-ring arrangement, where an O atom has inserted between E and Ni in both the 1-oxy species as well as the 2-oxy or sulfinate form. Fig. 7 displays representative structures highlighting the NiFe core. As indicated the Ni⋯Fe distance in the 4-membered Ni(μS)(μE)Fe core is only slightly larger for E = Se vs. E = S. Expansion to 3.568 Å occurs in the 5-membered Ni–S–Fe–Se–O ring and to 3.395 Å for the analogous the Ni–S–Fe–S'–O ring in the 2-oxy species. The 5-membered rings in the selenium and sulfur forms are largely the same as the additional oxygen in the latter projects outside of the 5-membered ring.^{49,50} Notably the 2-oxy species and the 1-oxy sulfur species have been detected by mass spectroscopy but are not isolated sufficiently pure for XRD determinations. Interesting features in these

reactions and products include (a) the more rapid reaction of O₂ with the Se as compared to the S analogues; (b) oxygen partitioning in S vs. Se analogues; (c) the position of the oxygen-inserted products between E and Fe, or E and Ni; and (d) the mechanism of O₂ addition.

Analysis of the protein crystal structures described in the introduction to this Perspective finds, at this time, only one case of a 2-oxy selenocysteine within an oxygen-damaged [NiFeSe]–H₂ase active site, Scheme 2. In the natural system, the two oxygen atoms bridge between Fe and Se. In contrast, our biomimetic study finds primarily 1-oxy products for the selenium complex, but faster reactions as compared to the sulfur analogue that generates both 1- and 2-oxy species.⁵⁰

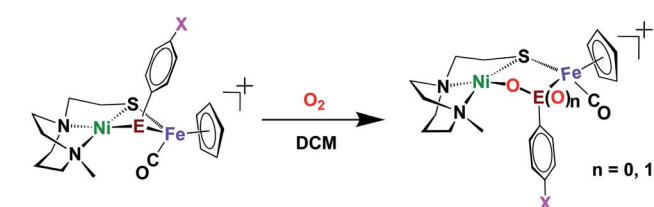

Scheme 3 Oxygenation reaction of Ni(μ-ER)Fe complexes.⁵⁰


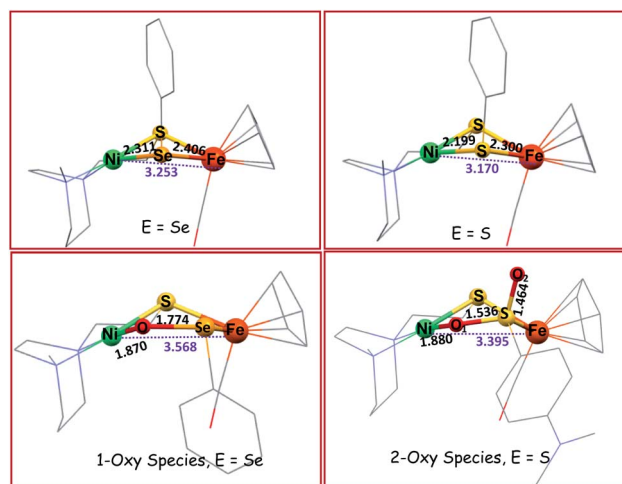


Fig. 7 Solid state XRD molecular structures of NiFe complexes.^{49,50}



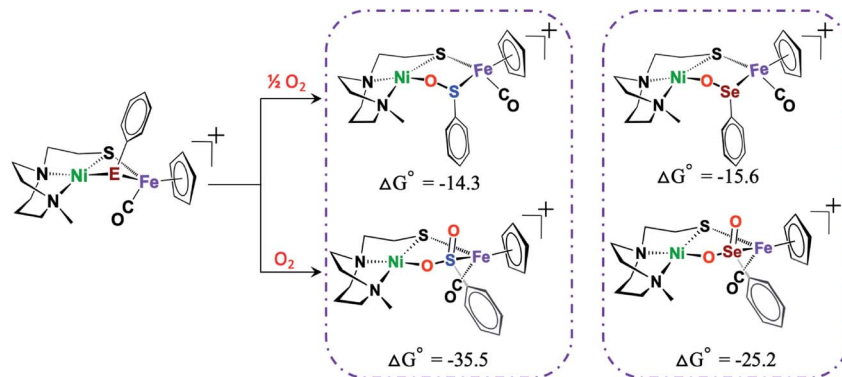

Scheme 4 DFT calculated free energy values, ΔG° , for comparison of oxygen-uptake reactions of $\text{Ni}(\mu\text{-E}_{\text{PhH}})(\mu\text{-S}'_{\text{N}_2})\text{Fe}$ complexes, E = S and Se, in kcal mol^{-1} .⁵⁰


To reiterate, several 2-oxy sulfinato species have been discovered in various oxygen-damaged $[\text{NiFeS}]\text{-H}_2\text{ase}$ structures, but 2-oxy selenoates are rare. A computational study in collaboration with M. B. Hall and L. C. Elrod pursued a thermodynamic approach to address this dichotomy.⁵⁰ Scheme 4 shows that for both $[\text{NiFeS}]\text{-}$ and $[\text{NiFeSe}]\text{-H}_2\text{ases}$ model complexes that explore differences for S vs. Se, the 2-oxy species are thermodynamically favored, for both S and Se, the difference between the 1-oxy and 2-oxy species is around 10 kcal in Se analogue and 20 kcal in the S version. However, comproportionation of the 2-oxy with the 0-oxy selenium species to generate two 1-oxy products is favored by -6 kcal. The analogous comproportionation for the sulfur species is thermodynamically disfavored, as the reaction is uphill by $+6.9$ kcal. That is, the 2-oxy sulfinate more readily forms and is likely to remain in this form.⁵⁰

Computations also agree the observation that the bridging-S that is tethered to the N of the diazacycle are disfavored to become oxygenated. A computational cleavage of the tether

results in a $15 \text{ kcal mole}^{-1}$ lowering of the oxygenated sulfur, and a preference for it over the S of the PhS.⁴⁹

While various ratios of 1- and 2-oxy species are found in the oxygenation reactions of most -E-Ph-X derivatives in this family of complexes, the thiolate of greater basicity, $\text{-SC}_6\text{H}_4\text{NH}_2$, shows selectivity for the 2-oxy species.⁵⁰ Such a result provided opportunity to explore one aspect of the mechanism of O_2 addition *via* isotope distribution reactions, as presaged in O_2 addition studies of the monomeric NiN_2S_2 species.^{32,33} An isotopic labeling/mass spectroscopy experiment analyzing products from a mixture of $^{32}\text{O}_2/^{36}\text{O}_2$ found the two oxygens on $\text{-S(O)}_2\text{C}_6\text{H}_4\text{NH}_2$ are from the same O_2 molecule, consistent with a concerted dioxygen addition reaction.⁵⁰ If analogous to the concerted addition of $^{32}\text{O}_2/^{36}\text{O}_2$ earlier studied, this result suggests O_2 binding at Ni as precursor to its transfer to the chalcogen. However the nuclearity of the complex that takes up the O_2 is as unknown as is the fate of the second oxygen in the 1-oxy species.

The possibility of reversal of oxygenated damage was explored using both chemical deoxygenation, O-abstrating

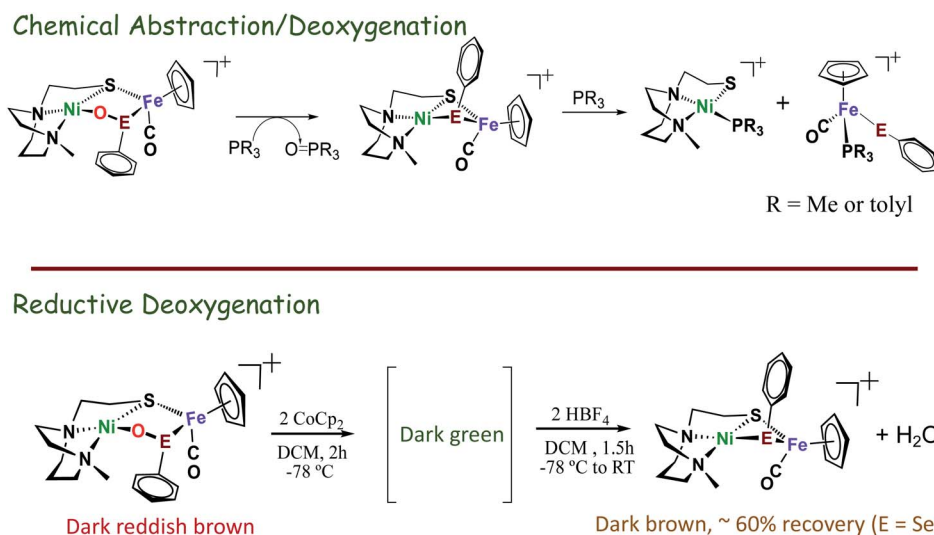

Scheme 5 Oxygen removal from oxy-species by O-abstrating agents, PR_3 (R = Me, or *o*-tolyl), or when using CoCp_2 as reductant and HBF_4 as proton source.^{49,50}




agents, PR_3 ($\text{R} = \text{Me}$, or *o*-tolyl), and the “electrochemical” deoxygenation, by using CpCo_2 as reductant and HBF_4 as proton source. Both methods realize oxygen removal from the 1-oxy species giving spectroscopic yield of 60%, however, the 2-oxy compounds are inert.^{49,50} Mass spectra and infrared spectra confirmed the oxygen removal from 1-oxy species; and proton NMR spectroscopy indicated the oxygen was removed as H_2O (Scheme 5).

4. O_2 -damage studies on models for $[\text{FeFe}]\text{-H}_2$ ases active sites

While the $[\text{NiFe}]\text{-H}_2$ ases and the model complexes show reversible O-uptake and removal at S and Se, no S-oxy species have been found in structures of the $[\text{FeFe}]\text{-H}_2$ ase. Compared to $[\text{NiFe}]\text{-H}_2$ ases, the $[\text{FeFe}]\text{-H}_2$ ases are much less oxygen tolerant.⁵² Adventitious O_2 diffuses through the gas channel in the protein and appears to first land on the vacant site at the distal Fe_d , which is remote from the $4\text{Fe}4\text{S}$ cubane. The ROS forms from the attack and further results in the diffusion and destruction of the $4\text{Fe}4\text{S}$ subcluster.^{52,53} Recent crystallographic studies on $[\text{FeFe}]\text{-H}_2$ ases from the Happe group show the Fe_d dissociation and loss on exposure to O_2 .⁵⁴

Although there is no evidence of oxygen protection by S in $[\text{FeFe}]\text{-H}_2$ ases, biomimetics based on the ubiquitous diiron complexes, $(\mu\text{-pdt})[\text{Fe}(\text{CO})_2\text{L}][\text{Fe}(\text{CO})_2\text{L}']$ ($\text{L}/\text{L}' = \text{CO}$, PPh_3 , or PMe_3), form sulfenates at the propanedithiolate sulfurs on reaction with O-atom sources such as H_2O_2 , or *meta*-chloroperoxybenzoic acid, as shown in Scheme 6a.⁵⁵ Deoxygenation with reclamation of the binding dithiolate occurs with addition of Cp^*_2Co and H_2O . More details can be found in a 2011 microreview by Darensbourg and Weigand in *Eur. J. Inorg. Chem.*⁵⁶

Dey, *et al.*, reported an interesting role for the $\mu\text{-SRS}$ cofactor in the complex $(\mu\text{-S}_2(\text{CH}_2)_2\text{NAr})[\text{Fe}(\text{CO})_3]_2$. On replacement of the $-\text{CH}_2-$ group in $(\mu\text{-pdt})[\text{Fe}(\text{CO})_2\text{L}][\text{Fe}(\text{CO})_2\text{L}']$ with a secondary amine bridgehead, H_2 production was possible in

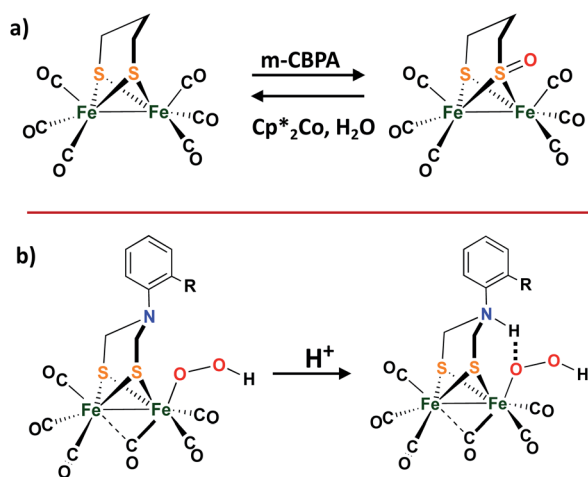

Scheme 6 (a) The sulfur oxygenation in model complex of $[\text{FeFe}]\text{-H}_2$ ases; (b) Proposed protonated bridging nitrogen reduction by *ortho*-substituted ADT-bridged $[\text{FeFe}]\text{-H}_2$ ases mimics.^{57,58}

the presence of dissolved O_2 in water ($\text{pH} = 5.5$).^{57,58} It is proposed that the bridgehead *N*-protonation and subsequent H-bonding capability assists SO-O bond cleavage which accounts for O_2 tolerance, as shown in the Scheme 6b.⁵⁸

5. Advances in technological development: O_2 -protection provided by protective polymer films layer in films

Clearly the protein matrix offers much more than the physical protection of the active sites of H_2 ase's from O_2 that was simplistically described early in this manuscript. The ability to maintain activity in the presence of O_2 exists for many enzymes and the importance of understanding such a desirable characteristic is vital for practical applications both of enzymes and of biomimetics. Artificial methods to increase oxygen tolerance and extend the lifetimes of such hydrogenases and synthetic analogues of their active sites, while using them in H_2 production/oxidation have long been sought and a full description of this field is beyond the scope of our Perspective. Recent developments addressing such challenges describe devices designed both for practicality and for interrogating best approaches to their improvement. As example, redox polymers have been employed as a protective film over $[\text{NiFe}]\text{-H}_2$ ase, isolated from *D. vulgaris* Miyazaki F by an collaborative efforts of Plumere, Rudiger, Schuhmann, Lubitz *et al.*⁵⁹ By adding a redox hydrogel film, consisting of a viologen-functionalized polymer over the O_2 -sensitive catalyst layer on the electrode surface, the device is able to efficiently work and produce hydrogen under $\sim 5\%$ O_2 . Subsequently, a paradigm shift was made on observing improved efficiency when the size of the thick film ($>100 \mu\text{m}$) was reduced to thin films (down to as much as $3 \mu\text{m}$).⁶⁰ That is, they uncovered the precise conditions that balanced the competition for electrons needed for current generation and those needed for the O_2 protection process. The contributions from kinetics of H_2 oxidation and for O_2 consumption were fit to a mathematical model that included diffusion of the oxidized enzyme back to the electrode within regimes in the film, explaining the advantages of the thin film. The basis of such protection is the ability of the redox viologen-functionalized polymer to rapidly divert electrons from the inner catalyst layer and use them for O_2 reduction, in this way protecting the inner catalyst film from oxygen attack. The role of the extra redox protecting matrix is actually “similar” to the $[4\text{Fe}3\text{S}]$ cluster adopted in membrane-bound hydrogenase (MBH); the latter provides extra two electrons to reduce oxygen.

Electrode disposition also plays a role in oxygen protection of model complexes for $[\text{NiFe}]$ and $[\text{NiFeSe}]\text{-H}_2$ ases. The Ni site models, $[\text{Ni}(\text{L}^{\text{E}})(\text{Mes}^{\text{E}})]^-$ ($\text{E} = \text{S}$ or Se), reported by Reisner, are decomposed under oxygen and form disulfides/diselenides.⁸ However, they are precursors for oxygen-tolerant catalysts for heterogeneous H_2 production by depositing on the electrode.⁶¹



6. Concluding remarks

While systematic changes in ligand properties hoping to distinguish first coordination sphere contributions from “sterics vs. electronics” are widely desirable in accounting for the efficacy of a homogeneous metallo-catalyst, rarely are chemists presented with such a controlled coordination environment as is found in the two enzyme active sites described above. The modification of a single atom in the [NiFeS]– vs. [NiFeSe]–H₂ase active site, resulted in profound differences in activity, in oxygen tolerance, and in structures of O-damaged active sites can be largely rationalized based on fundamental differences between sulfur and selenium. From our perspective the few NiFe models of those sites have informed on the value of Nature's well-designed active sites comprised of two metals, which permit various levels of O₂ uptake because of the varying O-affinity of the S and Se based ligand, preventing untenable metal oxidation. Such M–Se–O–M' and M–S–O–M' species appear to be transient O-atom depositories which provide a chance for repair or O-atom removal, without drastic damage to the protein. Clearly the biomimetic complexes are limited at this time and they are flawed, *i.e.*, their structures lack features assumed to be critical to the efficient functioning of the active sites.

Selenium wins in both the hydrogen-processing catalytic ability and in recovery from O-damage. Yet it has downsides to wider use in nature because of (1) geographic availability (the ratio of S over Se is as low as 6000 : 1 and as high as 55 500 : 1²⁶); and (2) the ease – or lack thereof—of biosynthetic machinery for the incorporation of selenocysteine into proteins. For example, to recode the stop codon UGA to a sense codon for Selenocysteine in the Eukaryotic Sec-insertion machinery, several accessory proteins and ATP units are required²⁶. We stress that the critical studies from Portugal that compared [NiFeS]– and [NiFeSe]–H₂ase were based on single site mutations of the latter that essentially converted the [NiFeSe]–H₂ase in *D. vulgaris* Hildenborough into the identical protein except with Se replaced by S. The reverse process (S → Se), cannot be readily performed. The significance of this work is that the only difference in the hydrogenase studied was the active sites; everything else was the same. Hence any differences were due to the single chalcogen atom. Those differences are comfortably explained by the physical properties of the elements themselves, although subtle changes in protein structure could arguably propagate into a different controlling feature.

A final note is directed towards the protective, anti-oxidant, value of selenium. The studies we described all involve the chalcogens in the first coordination sphere of the NiFe moieties. Studies that explore differences induced by placing selenium in second or third coordination spheres have yet to be done. Could selenium be a watch dog or guard for O₂ invasion in general air-sensitive molecular catalysts? At what distance would such a guard need to be placed? This is an intriguing question for future synthetic or post-translational designs.

The very specific interactions of residues in the protein polymer that account for the slight distortion in the

coordination geometry of the active sites structures from solution forms also permit changes that occur with substrate binding and activation. This role of the protein matrix is beginning to be understood with more clarity for the hydrogenases as these organometallic active sites, especially the [FeFe]–H₂ase, have fewer restrictions from covalent attachments. The matrix provided by the redox-active polymer films, discussed in the last part of this manuscript holds much interest for the possibility of practical application both of enzymes and of fragile biomimetics of the active sites.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financial supported by the National Science Foundation (CHE-1665258) and the Robert A. Welch Foundation (A-0924). The authors express appreciation to colleagues and coworkers through the years, especially Professor M. B. Hall of TAMU.

Notes and references

- 1 J. W. Peters, W. N. Lanzilotta, B. J. Lemon and L. C. Seefeldt, *Science*, 1998, **282**, 1853–1858.
- 2 A. Volbeda, M. H. Charon, C. Piras, E. C. Hatchikian, M. Frey and J. C. Fontecilla-Camps, *Nature*, 1995, **373**, 580–587.
- 3 E. Garcin, X. Vernede, E. C. Hatchikian, A. Volbeda, M. Frey and J. C. Fontecilla-Camps, *Structure*, 1999, **7**, 557–566.
- 4 S. Shima and R. K. Thauer, *Chem. Rec.*, 2007, **7**, 37–46.
- 5 H. Ogata, K. Nishikawa and W. Lubitz, *Nature*, 2015, **520**, 571–574.
- 6 W. Lubitz, H. Ogata, O. Rudiger and E. Reijerse, *Chem. Rev.*, 2014, **114**, 4081–4148.
- 7 R. M. Evans, E. J. Brooke, S. A. Wehlin, E. Nomerotskaia, F. Sargent, S. B. Carr, S. E. Phillips and F. A. Armstrong, *Nat. Chem. Biol.*, 2016, **12**, 46–50.
- 8 C. Wombwell, C. A. Caputo and E. Reisner, *Acc. Chem. Res.*, 2015, **48**, 2858–2865.
- 9 D. M. Heinekey, *J. Organomet. Chem.*, 2009, **694**, 2671–2680.
- 10 H. Ogata, P. Kellers and W. Lubitz, *J. Mol. Biol.*, 2010, **402**, 428–444.
- 11 H. Ogata, S. Hirota, A. Nakahara, H. Komori, N. Shibata, T. Kato, K. Kano and Y. Higuchi, *Structure*, 2005, **13**, 1635–1642.
- 12 T. Buhre, O. Lenz, N. Krauss and B. Friedrich, *J. Biol. Chem.*, 2005, **280**, 23791–23796.
- 13 S. Zacarias, A. Temporão, M. d. Barrio, V. Fourmond, C. Léger, P. M. Matias and I. A. C. Pereira, *ACS Catal.*, 2019, **9**, 8509–8519.
- 14 M. C. Marques, C. Tapia, O. Gutierrez-Sanz, A. R. Ramos, K. L. Keller, J. D. Wall, A. L. De Lacey, P. M. Matias and I. A. C. Pereira, *Nat. Chem. Biol.*, 2017, **13**, 544–550.



- 15 P. Rodríguez-Maciá, L. M. Galle, R. Bjornsson, C. Lorent, I. Zebger, Y. Yoda, S. P. Cramer, S. DeBeer, I. Span and J. A. Birrell, *Angew. Chem., Int. Ed. Engl.*, 2020, **59**, 2–11.
- 16 Y. Shomura, K. S. Yoon, H. Nishihara and Y. Higuchi, *Nature*, 2011, **479**, 253–256.
- 17 A. Volbeda, P. Amara, C. Darnault, J. M. Mouesca, A. Parkin, M. M. Roessler, F. A. Armstrong and J. C. Fontecilla-Camps, *Proc. Natl. Acad. Sci. U. S. A.*, 2012, **109**, 5305–5310.
- 18 J. Fritsch, P. Scheerer, S. Frielingsdorf, S. Kroschinsky, B. Friedrich, O. Lenz and C. M. Spahn, *Nature*, 2011, **479**, 249–252.
- 19 C. Gebner, O. Trofanchuk, K. Kawagoe, Y. Higuchi, N. Yasuoka and W. Lubitz, *Chem. Phys. Lett.*, 1996, **256**, 518–524.
- 20 S. Foerster, M. Stein, M. Brecht, H. Ogata, Y. Higuchi and W. Lubitz, *J. Am. Chem. Soc.*, 2003, **125**, 83–93.
- 21 A. Volbeda, L. Martin, C. Cavazza, M. Matho, B. W. Faber, W. Roseboom, S. P. Albracht, E. Garcin, M. Rousset and J. C. Fontecilla-Camps, *J. Biol. Inorg. Chem.*, 2005, **10**, 239–249.
- 22 A. Volbeda, L. Martin, E. Barbier, O. Gutiérrez-Sanz, A. L. D. Lacey, P. P. Liebgott, S. b. Dementin, M. Rousset and J. C. Fontecilla-Camps, *J. Biol. Inorg. Chem.*, 2014, **20**, 11.
- 23 A. Volbeda, P. Amara, M. Iannello, A. L. De Lacey, C. Cavazza and J. C. Fontecilla-Camps, *Chem. Commun.*, 2013, **49**, 7061–7063.
- 24 M. C. Marques, R. Coelho, A. L. De Lacey, I. A. Pereira and P. M. Matias, *J. Mol. Biol.*, 2010, **396**, 893–907.
- 25 M. J. Maroney and R. J. Hondal, *Free Radicals Biol. Med.*, 2018, **127**, 228–237.
- 26 H. J. Reich and R. J. Hondal, *ACS Chem. Biol.*, 2016, **11**, 821–841.
- 27 A. C. McQuilken and D. P. Goldberg, *Dalton Trans.*, 2012, **41**, 10883–10899.
- 28 T. Arakawa, Y. Kawano, S. Kataoka, Y. Katayama, N. Kamiya, M. Yohda and M. Odaka, *J. Mol. Biol.*, 2007, **366**, 1497–1509.
- 29 V. E. Kaasjager, E. Bouwman, J. Reedijk, C. A. Grapperhaus, J. H. Reibenspies, J. J. Smee, M. Y. Darensbourg, A. Derecskei-Kovacs and L. M. Thomson, *Inorg. Chem.*, 2002, **41**, 1837.
- 30 C. A. Grapperhaus and M. Y. Darensbourg, *Acc. Chem. Res.*, 1998, **31**, 451.
- 31 P. J. Farmer, J. N. Verpeaux, C. Amatore, M. Y. Darensbourg and G. Musie, *J. Am. Chem. Soc.*, 1994, **116**, 9355.
- 32 C. A. Grapperhaus, M. Y. Darensbourg, L. W. Sumner and D. H. Russell, *J. Am. Chem. Soc.*, 1996, **118**, 1791–1792.
- 33 S. A. Mirza, M. Kumar, M. A. Pressler, R. O. Day and M. J. Maroney, *Inorg. Chem.*, 1993, **32**, 977–987.
- 34 M. J. Maroney, S. B. Choudhury, P. A. Bryngelson, S. A. Mirza and M. J. Sherrod, *Inorg. Chem.*, 1996, **35**, 1073–1076.
- 35 S. B. Choudhury, M. A. Pressler, S. A. Mirza, R. O. Day and M. J. Maroney, *Inorg. Chem.*, 1994, **33**, 4831–4839.
- 36 S. Ding, P. Ghosh, A. M. Lunsford, N. Wang, N. Bhuvanesh, M. B. Hall and M. Y. Darensbourg, *J. Am. Chem. Soc.*, 2016, **138**, 12920–12927.
- 37 P. Ghosh, M. Quiroz, N. Wang, N. Bhuvanesh and M. Y. Darensbourg, *Dalton Trans.*, 2017, **46**, 5617–5624.
- 38 T. Kishima, T. Matsumoto, H. Nakai, S. Hayami, T. Ohta and S. Ogo, *Angew. Chem., Int. Ed. Engl.*, 2016, **55**, 724–727.
- 39 T. Matsumoto, T. Kishima, T. Yatabe, K.-S. Yoon and S. Ogo, *Organometallics*, 2017, **36**, 3883–3890.
- 40 K. Kim, T. Matsumoto, A. Robertson, H. Nakai and S. Ogo, *Chem.-Asian J.*, 2012, **7**, 1394–1400.
- 41 S. Ogo, *Chem. Rec.*, 2014, **14**, 397–409.
- 42 S. Ogo, *Coord. Chem. Rev.*, 2017, **334**, 43–53.
- 43 N. J. Lindenmaier, S. Wahlefeld, E. Bill, T. Szilvasi, C. Eberle, S. Yao, P. Hildebrandt, M. Horch, I. Zebger and M. Driess, *Angew. Chem., Int. Ed. Engl.*, 2017, **56**, 2208–2211.
- 44 C. S. A. Baltazar, M. C. Marques, C. M. Soares, A. M. DeLacey, I. A. C. Pereira and P. M. Matias, *Eur. J. Inorg. Chem.*, 2011, **2011**, 948–962.
- 45 A. Parkin, G. Goldet, C. Cavazza, J. C. Fontecilla-Camps and F. A. Armstrong, *J. Am. Chem. Soc.*, 2008, **130**, 13410–13416.
- 46 K. Weber, T. Kramer, H. S. Shafaat, T. Weyhermuller, E. Bill, M. van Gastel, F. Neese and W. Lubitz, *J. Am. Chem. Soc.*, 2012, **134**, 20745–20755.
- 47 C. Wombwell and E. Reisner, *Chem.-Eur. J.*, 2015, **21**, 8096–8104.
- 48 S. A. Mirza, R. O. Day and M. J. Maroney, *Inorg. Chem.*, 1996, **35**, 1992–1995; *Inorg. Chem.*, 1996, **35**, 4.
- 49 X. Yang, L. C. Elrod, J. H. Reibenspies, M. B. Hall and M. Y. Darensbourg, *Chem. Sci.*, 2019, **10**, 1368–1373.
- 50 X. Yang, L. C. Elrod, T. Le, V. S. Vega, H. Naumann, Y. Rezenom, J. H. Reibenspies, M. B. Hall and M. Y. Darensbourg, *J. Am. Chem. Soc.*, 2019, **141**, 15338–15347.
- 51 R. M. Jenkins, M. L. Singleton, L. A. Leamer, J. H. Reibenspies and M. Y. Darensbourg, *Inorg. Chem.*, 2010, **49**, 5503–5514.
- 52 C. Lambertz, N. Leidel, K. G. Havelius, J. Noth, P. Chernev, M. Winkler, T. Happe and M. Haumann, *J. Biol. Chem.*, 2011, **286**, 40614–40623.
- 53 A. Kubas, C. Orain, D. De Sancho, L. Saujet, M. Sensi, C. Gauquelin, I. Meynial-Salles, P. Soucaille, H. Bottin, C. Baffert, V. Fourmond, R. B. Best, J. Blumberger and C. Leger, *Nat. Chem.*, 2017, **9**, 88–95.
- 54 J. Esselborn, L. Kertess, U. P. Apfel, E. Hofmann and T. Happe, *J. Am. Chem. Soc.*, 2019, **141**, 17721–17728.
- 55 T. Liu, B. Li, M. L. Singleton, M. B. Hall and M. Y. Darensbourg, *J. Am. Chem. Soc.*, 2009, **131**, 8296–8307.
- 56 M. Y. Darensbourg and W. Weigand, *Eur. J. Inorg. Chem.*, 2011, **2011**, 994–1004.
- 57 S. Dey, A. Rana, D. Crouthers, B. Mondal, P. K. Das, M. Y. Darensbourg and A. Dey, *J. Am. Chem. Soc.*, 2014, **136**, 8847–8850.
- 58 M. E. Ahmed, S. Dey, M. Y. Darensbourg and A. Dey, *J. Am. Chem. Soc.*, 2018, **140**, 12457–12468.
- 59 N. Plumere, O. Rudiger, A. A. Oughli, R. Williams, J. Vivekananthan, S. Poller, W. Schuhmann and W. Lubitz, *Nat. Chem.*, 2014, **6**, 822–827.
- 60 H. Li, D. Buesen, S. Dementin, C. Leger, V. Fourmond and N. Plumere, *J. Am. Chem. Soc.*, 2019, **141**, 16734–16742.
- 61 C. Wombwell and E. Reisner, *Dalton Trans.*, 2014, **43**, 4483–4493.

