

Fig. 2 Synthesis and structure of "eggs-in-an-egg-carton" complex 2·3. (a) Synthetic scheme and crystal structure of 2·3, which consists of discrete cages 2 and infinite framework 3. (b) Interlocked cage structure of 2, composed of two M_3L_2 units. Encapsulated two BF_4^- ions are omitted for clarity. (c) Infinite framework of 3 (top view), composed of the same M_3L_2 units.

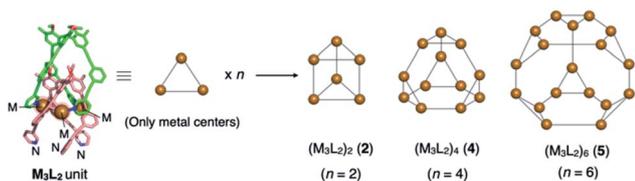


Fig. 3 Cartoon representation of the $(M_3L_2)_n$ oligomeric cages. The three metal centres of the common M_3L_2 subunit are extracted from each crystal structure. Depending on the assembly conditions, this subunit oligomerizes into dimeric, tetrameric, and hexameric cages (2, 4, and 5, respectively) by coordination of the free pyridyl nitrogen atoms of one subunit to the vacant metal centres (M) of the other subunits. For the complete structures, see the ESI† or our previous report.⁴

hexagonal pores (with *ca.* 18 Å of diameter based on Ag deposition, see the top view in Fig. 2c) that accommodate discrete cages 2 with good shape-complementarity. Interlayer distance of 3 along *c*-axis is 49 Å, which is fitted to the size of packed 2. All embedded cages 2 in one layer of porous sheets 3 have uniform chirality that arises from the helical orientation of the arms of ligand 1. The helicity of 1 in the next layer is reversed (as the top and middle layers in Fig. 2a), making co-crystal 2·3 centrosymmetric.†

Liquid-liquid diffusion is important for the formation of hybrid structure 2·3; we obtained only single crystals of the $(M_3L_2)_6$ hexameric cage (5 in Fig. 3) from its homogeneous

solution.⁴ Presumably, the liquid-liquid diffusion conditions produce a gradient in the local conditions of the mixture in the tube and allow oligomerization of the same M_3L_2 subunit into both discrete and infinite frameworks (2 and 3, respectively), which in turn co-crystallize into hybrid structure 2·3. It is interesting that the observed discrete cage is dimeric $(M_3L_2)_2$ cage 2, not the hexameric $(M_3L_2)_6$ cage 5 that was obtained under homogeneous conditions. We suppose that under the liquid-liquid diffusion conditions, kinetically formed dimeric cage 2 is incorporated into co-crystal 2·3 before it can be converted into thermodynamically favourable hexameric cage 5.

The common M_3L_2 subunits in 2 and 3 have similar capped structures, in which the two ligands (outer-1 and inner-1) are associated through weak acetylene-Ag(I) coordination (Fig. S2†). The three arms of outer-1 in 2 and 3 are almost superimposable. In contrast, those of inner-1 are oriented quite differently in 2 and 3. In 2, the three pyridyl nitrogen atoms are oriented such that the two subunits converge into the discrete structure, whereas those in 3 are directed at different angles to generate the extended coordination network (see Fig. 2b and c). This conformational adaptability is ascribed to the loose acetylene-Ag(I) coordination. In fact, there is a considerable difference in the geometry around the Ag(I) centres in 2 and 3 (average $\angle N1 \cdots Ag1 \cdots N2$ bend angle is 120° for 2 and 151° for 3; N1 and N2 are the pyridyl nitrogen atoms of outer-1 and inner-1, respectively).

Another type of discrete-infinite hybridization was achieved when similar tripodal ligand 6 (2.6 mM in nitromethane) with an $(OCH_2CH_2)_2OCH_3$ side chain (Fig. 4a) was complexed with $CuBF_4$ (3.8 mM), followed by slow vapour-diffusion crystallization with diethyl ether as a poor solvent. After the incubation at $3^\circ C$ for 2 weeks, the single crystals were obtained in moderate yield (61%). The framework of resulting discrete $(M_3L_2)_4$ tetrahedral cage 7 (with *ca.* 3.8 nm of each side length, analogous to cage 4 in Fig. 3; see also Fig. S3 and S4†) was revealed by single-crystal X-ray analysis. This discrete cage is co-crystallized with additional molecules of 6 that cross-link between cages of 7 by coordinating to one Cu(I) center in three neighbouring cages forming two-dimensional network (with intermetallic distances of 2.6 nm, Fig. 4b and c), exhibiting the composition of $[(Cu_3(6)_4(BF_4)_{12})_4](6)(solv)_n$. Considering the crystal packing of 6·7, geared configuration of two molecules of 6 (Fig. S4†) contributes to the cross-link, which is supported by dipole-dipole interactions and hydrogen bonding among alkoxy moieties of the introduced side chains and methoxy groups of the triarylmethane core. Consequently, two face-to-face networks are woven forming a bilayer (with thickness of 32 Å along *c*-axis) with the uniform chirality of the cage 7.‡

The cross-linked Cu(I) centres in 6 show tetrahedral geometry with a weakly π -coordinated acetylene moiety. The average $\angle N1 \cdots Cu1 \cdots N2$ bend angle of 99° is considerably smaller than that of the tri-coordinated Cu(I) centres (108° ; Fig. 4c). This large deviation in the bend angle demonstrates the structural flexibility and wide scope of the acetylene π -coordination. In network 6·7, five BF_4^- ions are encapsulated in the cavity of cage 7 (Fig. S5†); this is also observed in discrete capsule 4.⁴



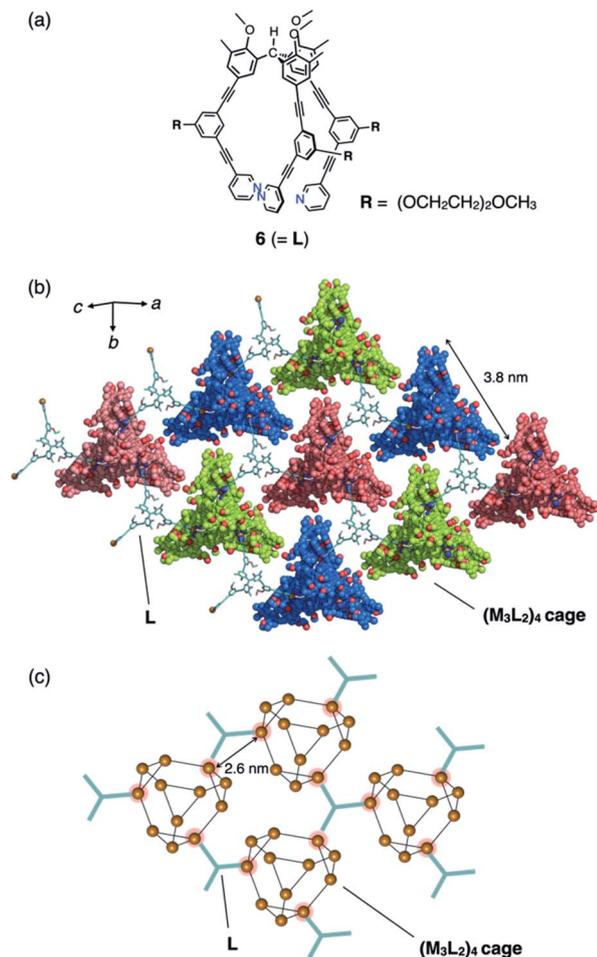


Fig. 4 (a) Chemical structure of tripodal ligand **6**. (b) Crystal structure of infinite coordination network **6·7**, in which discrete $(M_3L_2)_4$ cages are connected into a network. (c) Cartoon representation of network **6·7** showing the twelve Cu(I) centres in the discrete $(M_3L_2)_4$ cage extracted from the crystal structure.

Conclusions

In summary, we have synthesized discrete–infinite hybrid structures in which discrete cages with pre-determined cavities are included within infinite frameworks. Recent studies in the field of metal–organic frameworks (MOFs)⁷ and other infinite crystalline materials⁸ emphasize the importance of cavity design in porous coordination networks. We believe that embedding molecular hosts (with predetermined cavities as developed for host–guest chemistry and molecular recognition in solution)⁹ into infinite frameworks (with predetermined lattices) is a promising route to the construction of a diverse structures and properties of cavities in solid materials. The co-crystallization between discrete coordination cages and networked structures reported here is a unique example of this approach. Finally, we pay special attention to the loose acetylene–metal π -coordination because it allowed us to generate both the discrete and infinite frameworks from the same building unit at the same time and thus form the discrete–infinite co-crystal in a single step.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This research was supported by JSPS KAKENHI (19H05461 for M. F. and 19K05416 for Y. D.). The synchrotron X-ray crystallography was performed at the BL41XU and BL26B1 beamlines at SPring-8. We thank the Instrument Center at the Institute for Molecular Sciences (Okazaki, Japan) for providing access to the Bruker maxis mass spectrometer.

Notes and references

‡ Crystallographic data for **2·3**: $M = 4741.36$, trigonal, space group $P3_1c$, $a = b = 18.1553(5)$ Å, $c = 98.0140(10)$ Å, $V = 27978.6(16)$ Å³, $Z = 4$, $D_c = 1.126$ g cm⁻³, $T = 100(2)$ K, $0.818 < \theta < 19.502^\circ$, 8501 unique reflections out of 83 669 with $I > 2\sigma(I)$, GoF = 1.235, final R factors $R_1 = 0.0966$ ($I > 2\sigma(I)$), $wR_2 = 0.2921$, CCDC deposit number 1999248.

§ Crystallographic data for **6·7**: $M = 22030.43$, monoclinic, space group $C2/c$, $a = 67.657(10)$ Å, $b = 38.962(10)$ Å, $c = 67.631(10)$ Å, $V = 168 089(56)$ Å³, $Z = 4$, $D_c = 0.862$ g cm⁻³, $T = 293(2)$ K, $1.724 < \theta < 47.974^\circ$, 45 656 unique reflections out of 156 947 with $I > 2\sigma(I)$, GoF = 1.562, final R factors $R_1 = 0.1723$ ($I > 2\sigma(I)$), $wR_2 = 0.4172$, CCDC deposit number 1999249.

- (a) L. Chen, Q. Chen, M. Wu, F. Jiang and M. Hong, *Acc. Chem. Res.*, 2015, **48**, 201–210; (b) H. D. Mai, N. M. Tran and H. Yoo, *Coord. Chem. Rev.*, 2019, **387**, 180–198.
- (a) Y. Inokuma, T. Arai and M. Fujita, *Nat. Chem.*, 2010, **2**, 780–783; (b) F. Dai, J. Dou, H. He, X. Zhao and D. Sun, *Inorg. Chem.*, 2010, **49**, 4117–4124; (c) D. Luo, X.-P. Zhou and D. Li, *Angew. Chem., Int. Ed.*, 2015, **54**, 6190–6195; (d) W. M. Bloch, R. Babarao and M. L. Schneider, *Chem. Sci.*, 2020, **11**, 3664–3671; (e) Y. Kobayashi, M. Kawano and M. Fujita, *Chem. Commun.*, 2006, 4377–4379; (f) L. Shao, B. Hua, X. Hu, D. Stalla, S. P. Kelly and J. L. Atwood, *J. Am. Chem. Soc.*, 2020, **142**, 7270–7275; (g) L. Cao, P. Wang, X. Miao, Y. Dong, H. Wang, H. Duan, Y. Yu, X. Li and P. J. Stang, *J. Am. Chem. Soc.*, 2018, **140**, 7005–7011.
- (a) S. I. Swamy, J. Bacsá, J. T. A. Jones, K. C. Stylianou, A. Steiner, L. K. Ritchie, T. Hasell, J. A. Gould, A. Laybourn, Y. Z. Khimiyak, D. J. Adams, M. J. Rosseinsky and A. I. Cooper, *J. Am. Chem. Soc.*, 2010, **132**, 12773–12775; (b) L. Zhang, L. Xiang, C. Hang, W. Liu, W. Huang and Y. Pan, *Angew. Chem., Int. Ed.*, 2017, **56**, 7787–7791; (c) Y. Kin, J. Koo, I.-C. Hwang, R. D. Mukhopadhyay, S. Hong, J. Yoo, A. A. Dar, I. Kim, D. Moon, T. J. Shin, Y. H. Ko and K. Kim, *J. Am. Chem. Soc.*, 2018, **140**, 14547–14551; (d) J.-X. Ma, J. Li, Y.-F. Chen, R. Ning, Y.-F. Ao, J.-M. Liu, J. Sun, D.-X. Wang and Q.-Q. Wang, *J. Am. Chem. Soc.*, 2019, **141**, 3843–3848.
- Y. Domoto, M. Abe, T. Kikuchi and M. Fujita, *Angew. Chem., Int. Ed.*, 2020, **59**, 3450–3454.
- H. Lang, A. Jakob and B. Milde, *Organometallics*, 2012, **31**, 7661–7693.
- (a) A. Martín-Lasanta, L. Á. de Cienfuegos, A. Johnson, D. Miguel, A. J. Mota, A. Orte, M. J. Ruedas-Rama, M. Ribagorda, D. J. Cárdenas, M. C. Carreño,



- A. M. Echavarren and J. M. Cuerva, *Chem. Sci.*, 2014, **5**, 4582–4591; (b) J. D. Ferrara, A. Djebli, C. Tessier-Youngs and W. J. Youngs, *J. Am. Chem. Soc.*, 1988, **110**, 647–649; (c) T. Nishinaga, T. Kawamura and K. Komatsu, *Chem. Commun.*, 1998, 2263–2264; (d) H. V. R. Dias, J. A. Flores, J. Wu and P. Kroll, *J. Am. Chem. Soc.*, 2009, **131**, 11249–11255; (e) D. Parasar, R. M. Almotawa, N. B. Jayaratna, Y. S. Ceylan, T. R. Cundari, M. A. Omary and H. V. R. Dias, *Organometallics*, 2018, **37**, 4105–4118.
- 7 (a) D. Zhao, D. J. Timmons, D. Yuan and H.-C. Zhou, *Acc. Chem. Res.*, 2011, **44**, 123–133; (b) H. Furukawa, K. E. Cordova, M. O’Keeffe and O. M. Yaghi, *Science*, 2013, **341**, 1230444; (c) B. Le Ouay, S. Kitagawa and T. Uemura, *J. Am. Chem. Soc.*, 2017, **139**, 7886–7892; (d) M. Ding, R. W. Flaig, H.-L. Jiang and O. M. Yaghi, *Chem. Soc. Rev.*, 2019, **48**, 2783–2828.
- 8 (a) S.-Y. Ding and W. Wang, *Chem. Soc. Rev.*, 2013, **42**, 548–568; (b) P. J. Waller, F. Gándara and O. M. Yaghi, *Acc. Chem. Res.*, 2015, **48**, 3053–3063; (c) I. Hisaki, C. Xin, K. Takahashi and T. Nakamura, *Angew. Chem., Int. Ed.*, 2019, **58**, 11160–11170.
- 9 (a) M. M. Smulders, I. A. Riddell, C. Brown and J. R. Nitschke, *Chem. Soc. Rev.*, 2013, **42**, 1728–1754; (b) T. R. Cook and P. J. Stang, *Chem. Rev.*, 2015, **115**, 7001–7045; (c) C. J. Brown, F. D. Toste, R. G. Bergman and K. N. Raymond, *Chem. Rev.*, 2015, **115**, 3012–3035; (d) D. Zhang, T. K. Ronson and J. R. Nitschke, *Acc. Chem. Res.*, 2018, **51**, 2423–2436; (e) S. Pullen and G. H. Clever, *Acc. Chem. Res.*, 2018, **51**, 3052–3064.

