

## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)Cite this: *Nanoscale Adv.*, 2021, 3, 231**Fe<sub>7</sub>Se<sub>8</sub> encapsulated in N-doped carbon nanofibers as a stable anode material for sodium ion batteries†**Le Hu,<sup>‡a</sup> Chaoqun Shang,<sup>ID ‡\*a</sup> Xin Wang,<sup>ID \*abc</sup> and Guofu Zhou<sup>abc</sup>

Transition metal chalcogenides especially Fe-based selenides for sodium storage have the advantages of high electric conductivity, low cost, abundant active sites, and high theoretical capacity. Herein, we proposed a facile synthesis of Fe<sub>7</sub>Se<sub>8</sub> embedded in carbon nanofibers (denoted as Fe<sub>7</sub>Se<sub>8</sub>-NCFs). The Fe<sub>7</sub>Se<sub>8</sub>-NCFs with a 1D electron transfer network can facilitate Na<sup>+</sup> transportation to ensure fast reaction kinetics. Moreover, Fe<sub>7</sub>Se<sub>8</sub> encapsulated in carbon nanofibers, Fe<sub>7</sub>Se<sub>8</sub>-NCFs, can effectively adapt the volume variation to keep structural integrity during a continuous Na<sup>+</sup> insertion and extraction process. As a result, Fe<sub>7</sub>Se<sub>8</sub>-NCFs present improved rate performance and remarkable cycling stability for sodium storage. The Fe<sub>7</sub>Se<sub>8</sub>-NCFs exhibit practical feasibility with a reasonable specific capacity of 109 mA h g<sup>-1</sup> after 200 cycles and a favorable rate capability of 136 mA h g<sup>-1</sup> at a high rate of 2 A g<sup>-1</sup> when coupled with Na<sub>3</sub>V<sub>2</sub>(PO<sub>4</sub>)<sub>3</sub> to assemble full sodium ion batteries.

Received 26th October 2020  
Accepted 9th November 2020

DOI: 10.1039/d0na00897d

[rsc.li/nanoscale-advances](http://rsc.li/nanoscale-advances)**Introduction**

The economical concern of sodium ion batteries (SIBs) has made them one of the large scale energy storage systems to replace lithium ion batteries (LIBs).<sup>1,2</sup> Besides, SIBs have similar electrochemical storage properties to LIBs, which provides sufficient references for the exploration of electrode materials for SIBs.<sup>3,4</sup> Graphite as an anode employed in commercial LIBs exhibits undesirable sodium storage capability in SIBs with traditional carbonate-based electrolytes.<sup>5,6</sup> Therefore, the research of SIB anode materials is still a great challenge compared to the great progress of cathode materials with promising electrochemical performance.<sup>7,8</sup>

Over the past few years, tremendous efforts have been made to search for appropriate anode materials of SIBs, such as hard or soft carbon, alloy-type Sn/Sb/Bi, transition metal oxides/sulfides/phosphides/selenides, organic molecules, *etc.*<sup>9,10</sup> As potential candidates, transition metal selenides especially Fe-based selenides have the advantages of high electric conductivity, low cost, abundant active sites, and high theoretical capacity.<sup>11,12</sup> However,

the large radius of sodium ions results in sluggish reaction kinetics and large volume variation during sodium ion insertion/deinsertion and further hinders the rate capability and cycling stability of the corresponding SIBs.<sup>13,14</sup> To address these issues, downsizing the active materials to the nanoscale and surface coating to suppress the volume effect are common strategies.<sup>15,16</sup> For example, Chen *et al.* reported that micro-nano hierarchitectures of urchin-like Fe<sub>3</sub>Se<sub>4</sub> effectively display remarkable rate performance (200.2 mA h g<sup>-1</sup> at 30 A g<sup>-1</sup>).<sup>17</sup> Li and coworkers studied FeSe nanoparticles embedded in N-doped carbon (FeSe/N-C) with stable cycling performance (333.9 mA h g<sup>-1</sup> after 800 cycles).<sup>18</sup> Nevertheless, further improvement of the sodium storage capability of Fe-based selenides is still a challenge.

In this paper, we proposed a facile synthesis of Fe<sub>7</sub>Se<sub>8</sub> embedded in carbon nanofibers (denoted as Fe<sub>7</sub>Se<sub>8</sub>-NCFs), which was further assembled as an anode material for SIBs. Taking advantage of downsized dimensions, effective carbon buffer protection, and the 1D nanofiber electron transfer network, Fe<sub>7</sub>Se<sub>8</sub>-NCFs shows remarkable stability (232 mA h g<sup>-1</sup> at 0.1 A g<sup>-1</sup>, 400 cycles) and improved rate capability (153 mA h g<sup>-1</sup>, 2 A g<sup>-1</sup>) in half-cells. The electrochemical kinetic analysis unveils that the surface pseudocapacitive process contributes largely to the capacity, which undoubtedly enhances the rate capability. Moreover, Fe<sub>7</sub>Se<sub>8</sub>-NCFs coupled with Na<sub>3</sub>V<sub>2</sub>(PO<sub>4</sub>)<sub>3</sub> (denoted as NVP) also shows potential in full SIBs, which display favorable rate capability and reasonable reversible capacity.

**Experimental section****Preparation of Fe<sub>7</sub>Se<sub>8</sub>-NCFs nanofibers**

Polyacrylonitrile (PAN, 0.7 g) and iron(III) acetylacetonate (Fe(AcAc)<sub>3</sub>, 0.3 g) were mixed in dimethylformamide (DMF, 10

<sup>a</sup>Guangdong Provincial Key Laboratory of Optical Information Materials and Technology & Institute of Electronic Paper Displays, South China Academy of Advanced Optoelectronics, South China Normal University, Guangzhou 510006, China. E-mail: chaoqun.shang@ecs-scnu.org; wangxin@scnu.edu.cn

<sup>b</sup>National Center for International Research on Green Optoelectronics, South China Academy of Advanced Optoelectronics, South China Normal University, Guangzhou 510006, China

<sup>c</sup>International Academy of Optoelectronics at Zhaoqing, South China Normal University, Zhaoqing 526000, China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d0na00897d

‡ These authors contributed equally.

ml) by constantly stirring for 10 h to obtain a uniformly dispersed solution. Then, the as-prepared solution was put into a syringe and electrospun at a flow rate of  $0.1 \text{ mm min}^{-1}$  at high voltage (14 kV). The obtained  $\text{Fe}(\text{AcAc})_3/\text{PAN}$  nanofibers (0.1 g) and Se powder (0.2 g) were annealed at a temperature of  $500^\circ\text{C}$  for 4 h ( $\text{H}_2/\text{Ar}$ ). For the comparative sample,  $\text{Fe}_7\text{Se}_8$  powder was prepared by the same annealing process using  $\text{Fe}(\text{AcAc})_3$  and Se powder (weight ratio: 1 : 2). The N-doped carbon nanofibers (NCFs) were annealed by the same process using PAN nanofibers. NVP was prepared following a previous report.<sup>19</sup>  $\text{NaH}_2\text{PO}_4$  (0.85 g),  $\text{NH}_4\text{VO}_3$  (0.47 g) and citric acid (0.77 g) were dissolved in deionized water (60 ml) with continuous agitation. Graphene oxide (0.04 g) was mixed into the above solution and then freeze-dried for 24 h. The as-prepared powder was calcined at  $800^\circ\text{C}$  for 8 h ( $\text{Ar}/\text{H}_2$ ) to obtain NVP.<sup>20</sup> The material characterization section is in the ESI.<sup>†</sup>

### Electrochemical measurement

A slurry was prepared by mixing 80 wt% active material, 10 wt% Super P, and 10 wt% binder (polyvinylidene fluoride, PVDF) and was cast onto Cu foil and dried in a vacuum at  $60^\circ\text{C}$  for 12 h to prepare the working electrode. The working electrode was cut into discs with a diameter of 12 mm. The full cell consists of the  $\text{Fe}_7\text{Se}_8\text{-NCF}$  anode and NVP cathode. The NVP cathode was prepared by mixing NVP, Super P and polytetrafluoroethylene (PTFE) (weight ratio: 8 : 1 : 1). For the  $\text{NVP}||\text{Fe}_7\text{Se}_8\text{-NCFs}$  full cell, the mass ratio of the cathode and anode was controlled at 5 : 1. The electrolyte was  $\text{NaClO}_4$  (1 M) dissolved in a mixture of ethylene carbonate and dimethyl carbonate (volume ratio: EC/DMC = 1/1) solution with fluoroethylene carbonate (FEC: 5 vol%). Electrochemical impedance spectroscopy (EIS) measurements were performed in the frequency range from 100 kHz to 100 mHz. Cyclic voltammetry (CV) was performed on a BioLogic (VMP3) electrochemical workstation in the voltage range of 0.1–3 V.

## Results and discussion

The synthesis process of the  $\text{Fe}_7\text{Se}_8\text{-NCFs}$  nanofibers is mainly divided into electrospinning and subsequent selenization processes (Fig. S1<sup>†</sup>). The SEM image of as-electrospun  $\text{Fe}(\text{AcAc})_3/\text{PAN}$  shows smooth and evenly distributed nanofibers, as exhibited in Fig. 1a and b. After the selenization process,  $\text{Fe}_7\text{Se}_8\text{-NCFs}$  well maintains the 1D fiber structure of  $\text{Fe}(\text{AcAc})_3/\text{PAN}$  and regular distribution (Fig. 1c and d). The cross-sectional SEM images of  $\text{Fe}_7\text{Se}_8\text{-NCFs}$  show abundant voids between the nanofibers, which facilitate the penetration of the electrolyte (Fig. S2<sup>†</sup>). Combined with SEM morphologies, the TEM image further reveals that the diameter of  $\text{Fe}_7\text{Se}_8\text{-NCFs}$  nanofibers is about 200 nm, and the  $\text{Fe}_7\text{Se}_8$  nanoparticles are uniformly embedded in N-doped carbon nanofibers (Fig. 2a). The high-resolution TEM image (HRTEM, Fig. 2b) of  $\text{Fe}_7\text{Se}_8\text{-NCFs}$  shows a lattice fringe of 0.27 nm, indexed to the (203) plane of the  $\text{Fe}_7\text{Se}_8$  phase. The SEM image and energy dispersive spectroscopy (EDS) elemental mappings reveal Fe, Se, N and C elements uniformly distributed in the carbon nanofibers (Fig. 2c and d). However, in Fig. S3,<sup>†</sup> the as-prepared  $\text{Fe}_7\text{Se}_8$  bulk is composed of large aggregated particles due to lack of a fiber support.

Fig. 3a displays the XRD pattern of  $\text{Fe}_7\text{Se}_8\text{-NCFs}$  and bulk  $\text{Fe}_7\text{Se}_8$ . The major diffraction peaks at  $32.3^\circ$ ,  $42.0^\circ$  and  $50.2^\circ$  are assigned to the (203), (206) and (220) planes of  $\text{Fe}_7\text{Se}_8$  (PDF#33-0676). It should be noted that the XRD peaks of  $\text{Fe}_7\text{Se}_8\text{-NCFs}$  slightly shift to high  $2\theta$ . This indicates the existence of Se vacancies owing to the protection of the NCF substrate during selenization, which can enhance the electronic conductivity, guaranteeing fast electron transfer for  $\text{Na}^+$  insertion/extraction. The diffraction peaks of  $\text{Fe}_7\text{Se}_8\text{-NCFs}$  are broader than those of bulk  $\text{Fe}_7\text{Se}_8$ , which demonstrates the small crystal size of  $\text{Fe}_7\text{Se}_8$  in the NCF matrix. This is beneficial to shorten the sodium ion

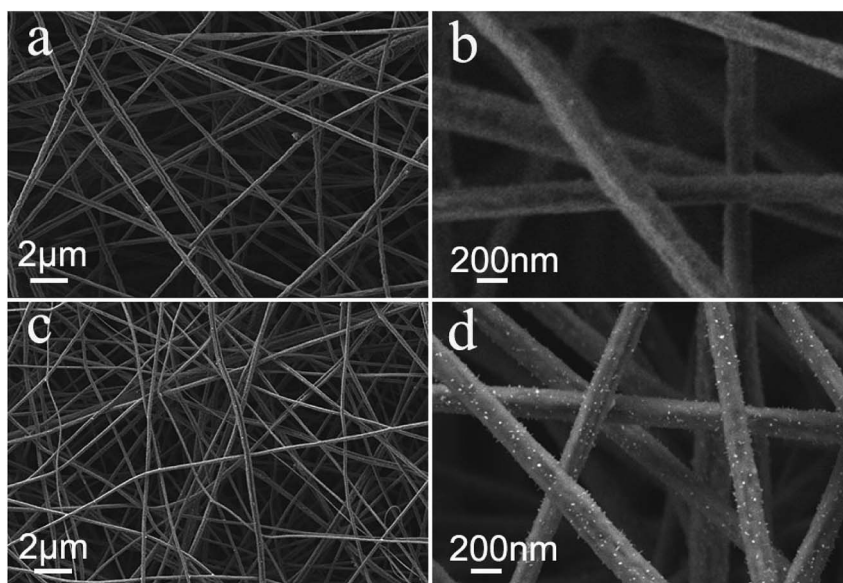


Fig. 1 (a and b) SEM images of  $\text{Fe}(\text{AcAc})_3/\text{PAN}$  nanofibers; (c and d) SEM images of as-prepared  $\text{Fe}_7\text{Se}_8\text{-NCFs}$ .



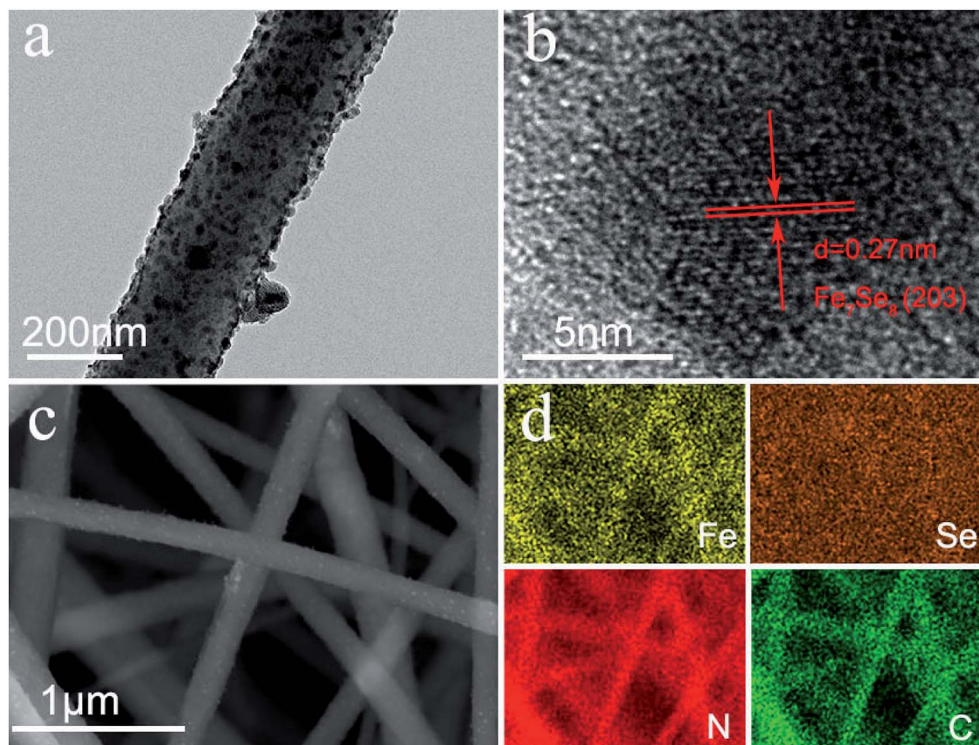


Fig. 2  $\text{Fe}_7\text{Se}_8$ -NCFs: (a) TEM; (b) HRTEM; (c) SEM image and (d) corresponding EDS mapping.

diffusion length during sodium ion insertion and deinsertion. According to the Scherrer formula (the details are in the ESI†), the crystal size of  $\text{Fe}_7\text{Se}_8$  in NCFs is  $\sim 20$  nm, while that of bulk  $\text{Fe}_7\text{Se}_8$  is 40 nm. The  $\text{Fe}_7\text{Se}_8$  content in the  $\text{Fe}_7\text{Se}_8$ -NCF composite was determined by a TGA test (Fig. S4a†). The mass loss below  $200^\circ\text{C}$  is due to the evaporation of the residual moisture in the  $\text{Fe}_7\text{Se}_8$ -NCF sample. The temperature between  $300$  and  $500^\circ\text{C}$  can be assigned to the oxidation of carbon fibers and  $\text{Fe}_7\text{Se}_8$ . When the temperature reaches  $600^\circ\text{C}$  in air, the final combustion product of  $\text{Fe}_7\text{Se}_8$ -NCFs is  $\text{Fe}_2\text{O}_3$  (Fig. S4b†).<sup>21</sup> Thus, the content of  $\text{Fe}_7\text{Se}_8$  in dried  $\text{Fe}_7\text{Se}_8$ -NCFs is  $\sim 20.6\%$ . An XPS test was performed to analyze the chemical composition of  $\text{Fe}_7\text{Se}_8$ -NCFs. The survey spectrum of  $\text{Fe}_7\text{Se}_8$ -NCFs illustrates the coexistence of Fe, Se, N and C elements in  $\text{Fe}_7\text{Se}_8$ -NCFs (Fig. S5a†). As presented in Fig. 3b, the Fe 2p spectrum can be divided into  $\text{Fe}^{2+}$  and  $\text{Fe}^{3+}$  for the spin-orbit doublet of Fe  $2p_{1/2}$  and Fe  $2p_{3/2}$ . The peaks at 725.2 and 713.5 eV are assigned to  $2p_{1/2}$  and  $2p_{3/2}$  of  $\text{Fe}^{2+}$ , and the peaks at 723.7 and 710.6 eV are ascribed to  $2p_{1/2}$  and  $2p_{3/2}$  of  $\text{Fe}^{3+}$ , demonstrating the presence of  $\text{Fe}^{2+}$  and  $\text{Fe}^{3+}$  states in  $\text{Fe}_7\text{Se}_8$ -NCFs.<sup>22</sup> In Fig. 3c, the XPS spectrum of Se 3d consists of Se  $3d_{3/2}$  (59.5 and 58.6 eV) and  $3d_{5/2}$  (56.3 and 55.7 eV).<sup>23</sup> In Fig. 3d, the C 1s spectra displays three peaks located at 288.4 eV (C=O), 286.4 eV (C-N), and 284.8 eV (C-C/C=C) respectively.<sup>24</sup> The N-doping carbon layer not only enhances electronic conductivity to promote fast reaction kinetics, but also relieves volume variation to keep the stable structure of  $\text{Fe}_7\text{Se}_8$ -NCFs during repeated cycling. The XPS spectrum and detailed analysis of other elements (O and N) are exhibited in Fig. S5.† In the Raman analysis, the peaks at

about 278, 330, and  $405\text{ cm}^{-1}$  might be assigned to Fe-Se bonds in  $\text{Fe}_7\text{Se}_8$ -NCFs, and other peaks at  $1358\text{ cm}^{-1}$  and  $1589\text{ cm}^{-1}$  are ascribed to the D band and G band, respectively<sup>25</sup> (Fig. S6†). The  $I_D/I_G$  of  $\text{Fe}_7\text{Se}_8$ -NCFs (1.76) and NCFs (1.64) indicates more defects of carbon on  $\text{Fe}_7\text{Se}_8$ -NCFs to promote reaction kinetics.

The electrochemical performance in sodium storage of  $\text{Fe}_7\text{Se}_8$ -NCFs was investigated by CV measurements (Fig. 4a). In the initial cycle, the sharp reduction peaks at 0.4 and 0.9 V originate from the generation of a solid electrolyte interface (SEI) film and irreversible  $\text{Na}^+$  insertion.<sup>26,27</sup> In the following curves, the broad redox peaks at 1.6 and 0.9 V are well overlapped, indicating a reversible conversion reaction for  $\text{Fe}_7\text{Se}_8$ -NCFs. The redox peaks of the CV curves are not obvious, which might be due to the carbon effect in  $\text{Fe}_7\text{Se}_8$ -NCFs. The 1D carbon fiber as a buffer matrix maintains the structural integrity to guarantee a long cycle life. In Fig. 4b, the charge/discharge profiles of  $\text{Fe}_7\text{Se}_8$ -NCFs show that the initial charge/discharge specific capacity is  $232/497\text{ mA h g}^{-1}$  and the corresponding initial coulombic efficiency (ICE) is 46.7%. The low ICE might be ascribed to solid electrolyte interface (SEI) formation and some irreversible side reactions, which are consistent with the CV result.<sup>28</sup> Fig. 4c depicts the cycling performance of  $\text{Fe}_7\text{Se}_8$ -NCFs compared with those of  $\text{Fe}_7\text{Se}_8$  and NCFs. When the current density is  $0.1\text{ A g}^{-1}$ ,  $\text{Fe}_7\text{Se}_8$ -NCFs delivers a reversible capacity of  $223\text{ mA h g}^{-1}$  after 400 cycles with a capacity retention rate of 96.5%, providing an impressive CE of around 100%. The comparative  $\text{Fe}_7\text{Se}_8$  displays a rapid decrease in current density from 359 to  $73\text{ mA h g}^{-1}$  during the 400 cycles. The high initial specific capacity of





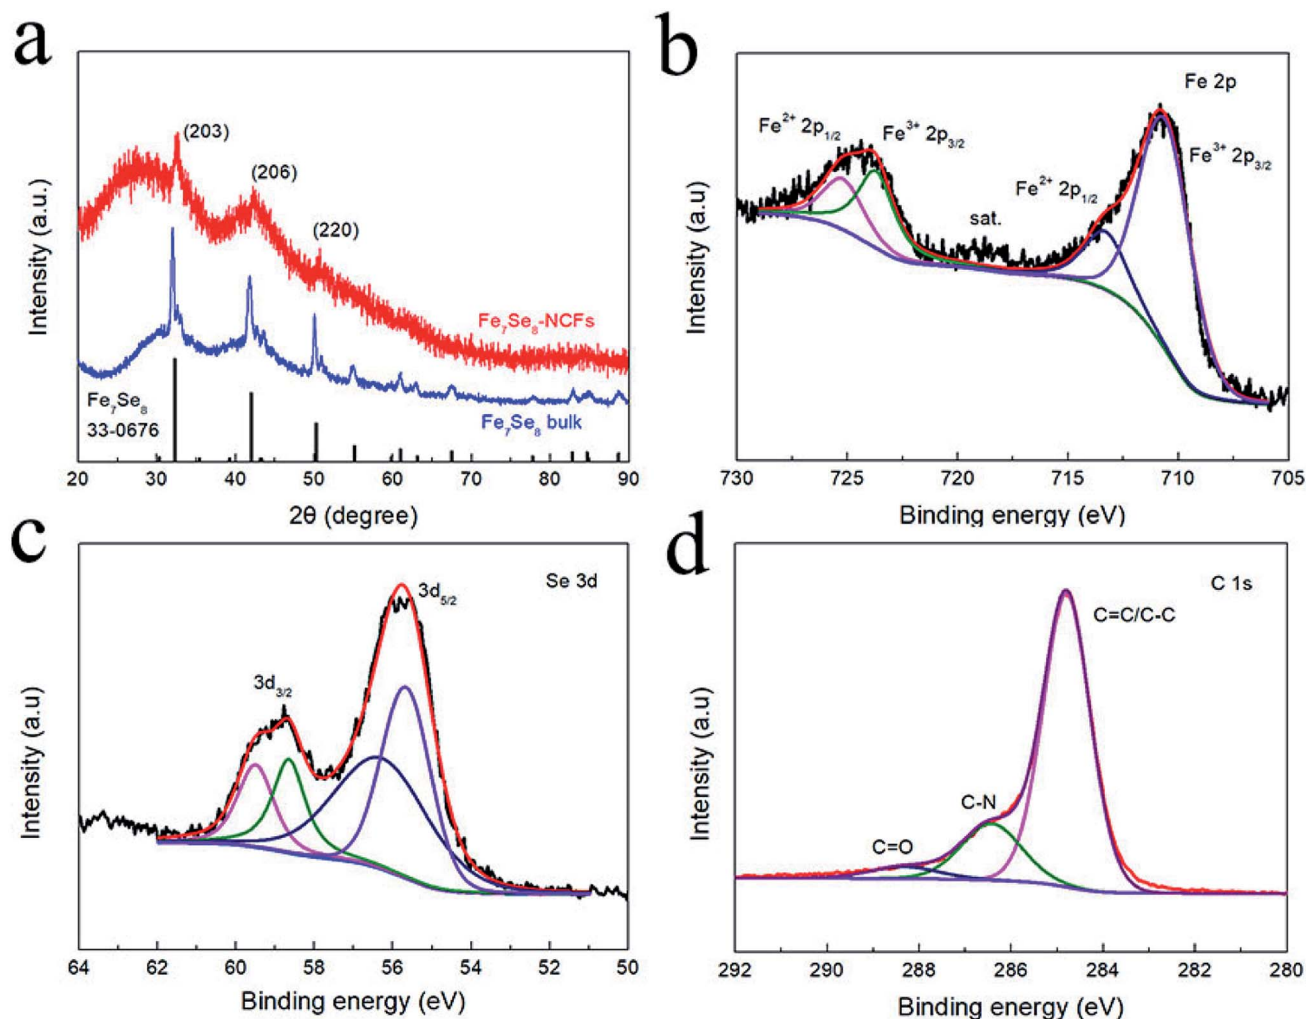


Fig. 3 (a) XRD pattern of Fe<sub>7</sub>Se<sub>8</sub>-NCFs. High-resolution XPS spectra of Fe<sub>7</sub>Se<sub>8</sub>-NCFs: (b) Fe 2p; (c) Se 3d; (d) C 1s.

comparative Fe<sub>7</sub>Se<sub>8</sub> is due to the high theoretical specific capacity of the Fe<sub>7</sub>Se<sub>8</sub> active material (419 mA h g<sup>-1</sup>). However, Fe<sub>7</sub>Se<sub>8</sub> undergoes serious volume change during larger Na<sup>+</sup> intercalation and deintercalation, which causes the active material to be pulverized with continuous capacity degradation. With the protection of NCFs, Fe<sub>7</sub>Se<sub>8</sub>-NCFs could adapt to volume expansion to retain a stable capacity. The rate capability of Fe<sub>7</sub>Se<sub>8</sub>-NCFs, Fe<sub>7</sub>Se<sub>8</sub> and NCFs is further tested and compared, as exhibited in Fig. 4d. As the current density increases from 0.1 to 2 A g<sup>-1</sup>, Fe<sub>7</sub>Se<sub>8</sub>-NCFs delivers a specific capacity of 237, 215, 195, 175 and 153 mA h g<sup>-1</sup>. Impressively, when the current density is switched back to 0.1 A g<sup>-1</sup>, Fe<sub>7</sub>Se<sub>8</sub>-NCFs recovers a specific capacity of 238 mA h g<sup>-1</sup> without any attenuation, demonstrating favorable rate performance of Fe<sub>7</sub>Se<sub>8</sub>-NCFs. In contrast, Fe<sub>7</sub>Se<sub>8</sub> shows poor rate performance (from 357 to 70 mA h g<sup>-1</sup> at 0.1 to 2 A g<sup>-1</sup>). The promising rate performance of Fe<sub>7</sub>Se<sub>8</sub>-NCFs could be attributed to the 1D carbon nanofibers, which can shorten the ion diffusion pathway to facilitate Na<sup>+</sup> transportation. As shown in Table S1,<sup>†</sup> the research of Fe<sub>7</sub>Se<sub>8</sub>-NCFs for sodium storage exhibits stable electrochemical performance.<sup>29</sup> Furthermore, Fig. 4e shows the

long-term cycling stability of Fe<sub>7</sub>Se<sub>8</sub>-NCFs with a specific capacity of 148 mA h g<sup>-1</sup> after 2000 cycles, which is more stable than those of Fe<sub>7</sub>Se<sub>8</sub> and NCFs (the current density: 2 A g<sup>-1</sup>). These results further reveal the strong structural stability of Fe<sub>7</sub>Se<sub>8</sub> encapsulated in 1D NCFs.

To deeply elucidate the stable carbon matrix structure of Fe<sub>7</sub>Se<sub>8</sub>-NCFs, the surface morphology of Fe<sub>7</sub>Se<sub>8</sub>-NCFs was observed before and after 100 cycles. The SEM morphology of fresh Fe<sub>7</sub>Se<sub>8</sub>-NCFs with regular nanofibers is shown in Fig. 5a. The cycled Fe<sub>7</sub>Se<sub>8</sub>-NCFs retains a flat and distinct 1D nanofiber structure with abundant voids (Fig. 5b), which is similar to the original shape. Meanwhile, the slight volume expansion of cycled Fe<sub>7</sub>Se<sub>8</sub>-NCFs might be due to the generation of a stable SEI film. These results suggest that the Fe<sub>7</sub>Se<sub>8</sub> embedded in a 1D carbon matrix can effectively alleviate the volume variation and maintain the structural integrity to guarantee a long cycle life. Additionally, the SEM image of fresh Fe<sub>7</sub>Se<sub>8</sub> has large bulk particles, as shown in Fig. 5c. After 100 cycles, Fe<sub>7</sub>Se<sub>8</sub> showed serious volume expansion compared with the pristine appearance (Fig. 5d), which is in accordance with the continuous capacity deterioration of Fe<sub>7</sub>Se<sub>8</sub> during cycling (Fig. 4c).



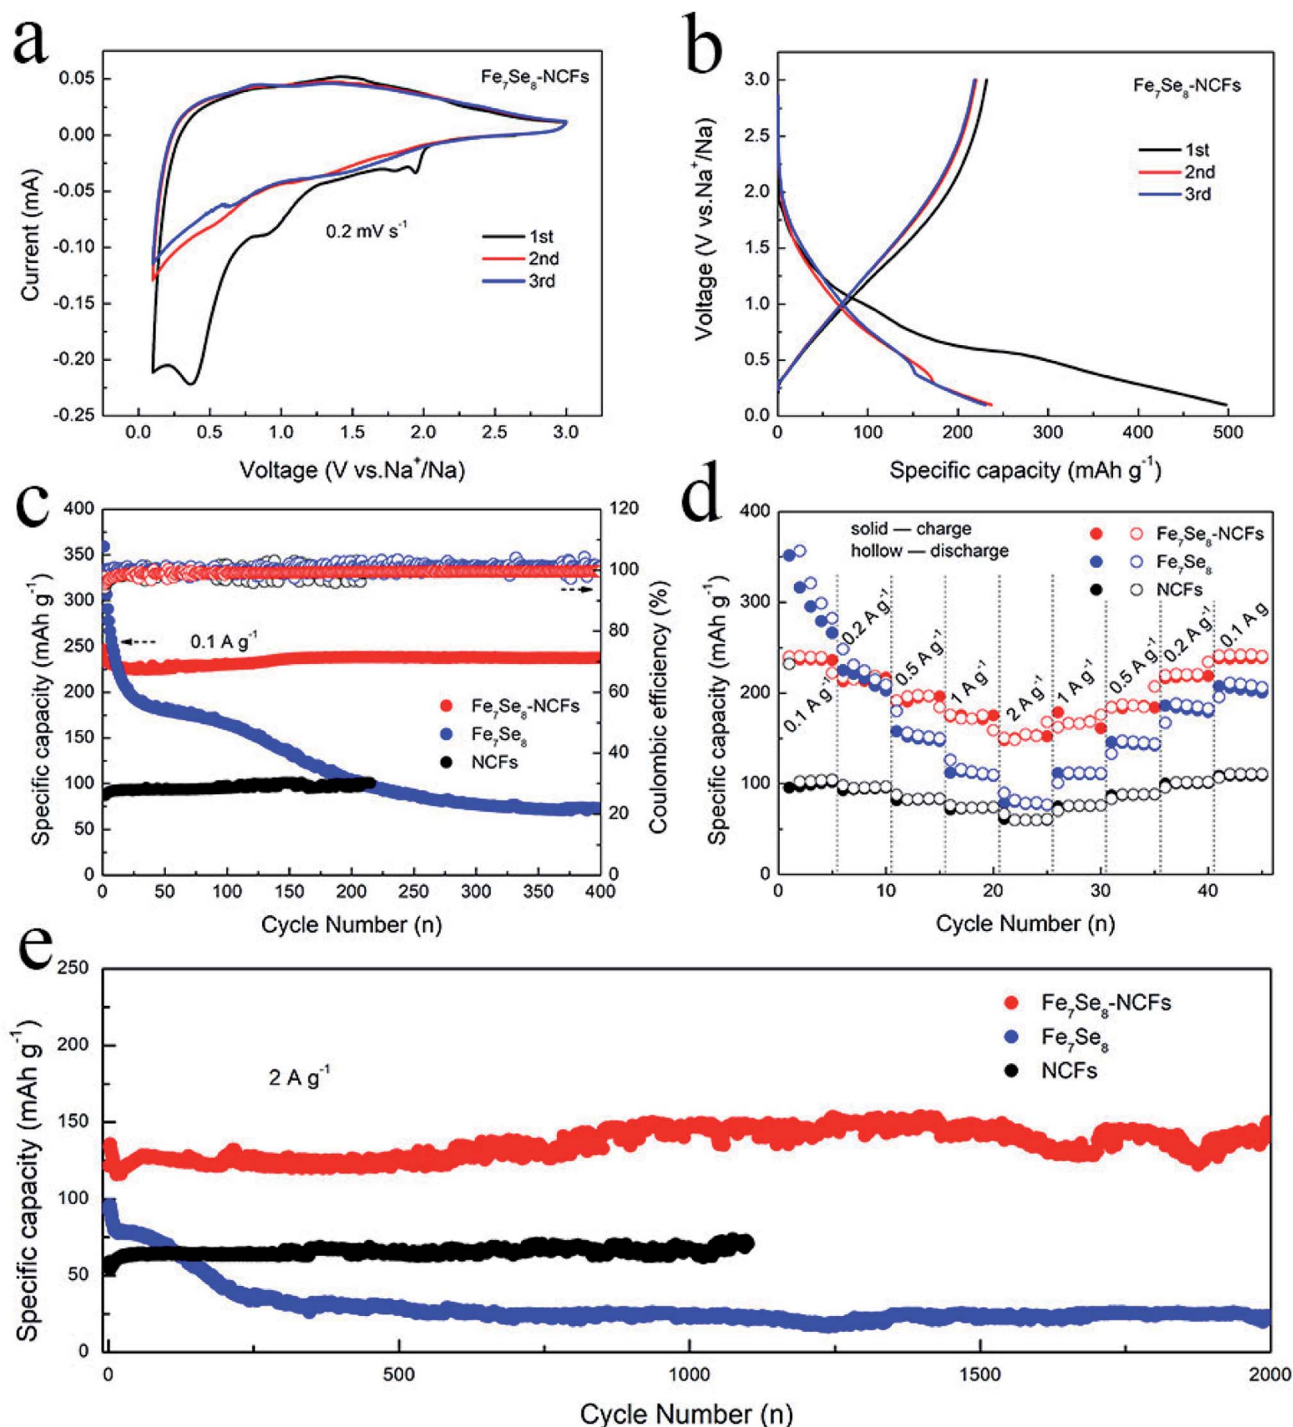


Fig. 4 (a) CV curves of Fe<sub>7</sub>Se<sub>8</sub>-NCFs and (b) charge/discharge curves of Fe<sub>7</sub>Se<sub>8</sub>-NCFs. Electrochemical performance of Fe<sub>7</sub>Se<sub>8</sub>-NCFs, Fe<sub>7</sub>Se<sub>8</sub> and NCFs: (c) cycling (0.1 A g<sup>-1</sup>); (d) rate; and (e) cycling performance (2 A g<sup>-1</sup>).

Fig. 6 displays the kinetics analysis of Fe<sub>7</sub>Se<sub>8</sub>-NCFs to understand the promising rate performance in sodium storage. When the scan rate increases from 0.2 to 1 mV s<sup>-1</sup>, the CV curves of Fe<sub>7</sub>Se<sub>8</sub>-NCFs and Fe<sub>7</sub>Se<sub>8</sub> show a similar shape (Fig. 6a and S7a†). The current ( $i$ ) and scan rate ( $v$ ) conform to the equation as follows:<sup>30,31</sup>

$$i = av^b \quad (1)$$

$$\log(i) = \log(a) + b \log(v) \quad (2)$$

The  $b$  value is the slope of eqn (2), which is in the range from 0.5 to 1. In general, a  $b$  value of 0.5 or 1 represents a capacitive-controlled or diffusion-controlled process. For Fe<sub>7</sub>Se<sub>8</sub>-NCFs, the  $b$  value of oxidation and reduction peaks is calculated to be 0.89, 0.95 and 0.88, higher than those of Fe<sub>7</sub>Se<sub>8</sub> (0.51, 0.51 and 0.55)



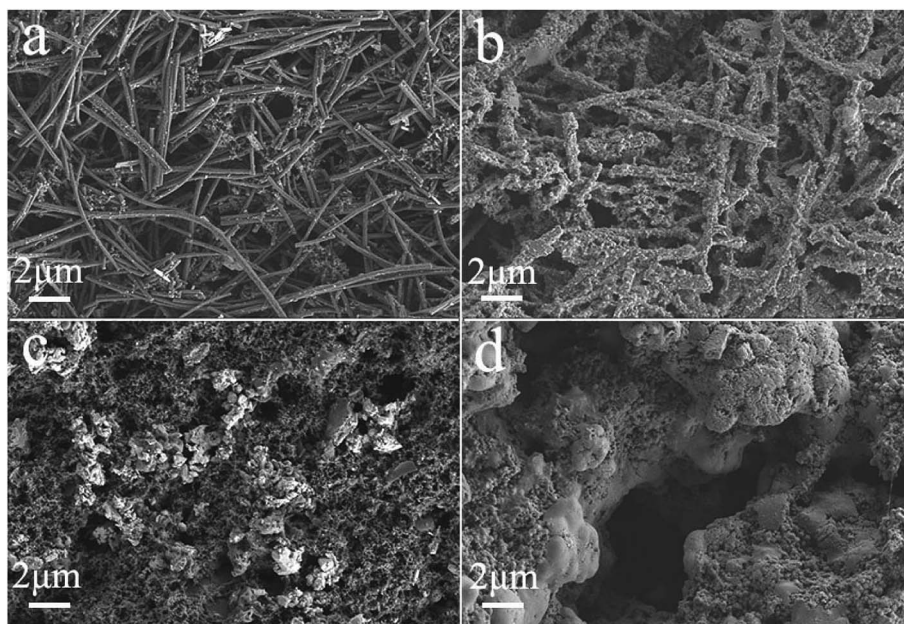


Fig. 5 SEM images of  $\text{Fe}_7\text{Se}_8\text{-NCFs}$  and  $\text{Fe}_7\text{Se}_8$ : (a and c) before cycling; (b and d) after 100 cycles in the charged state, respectively.

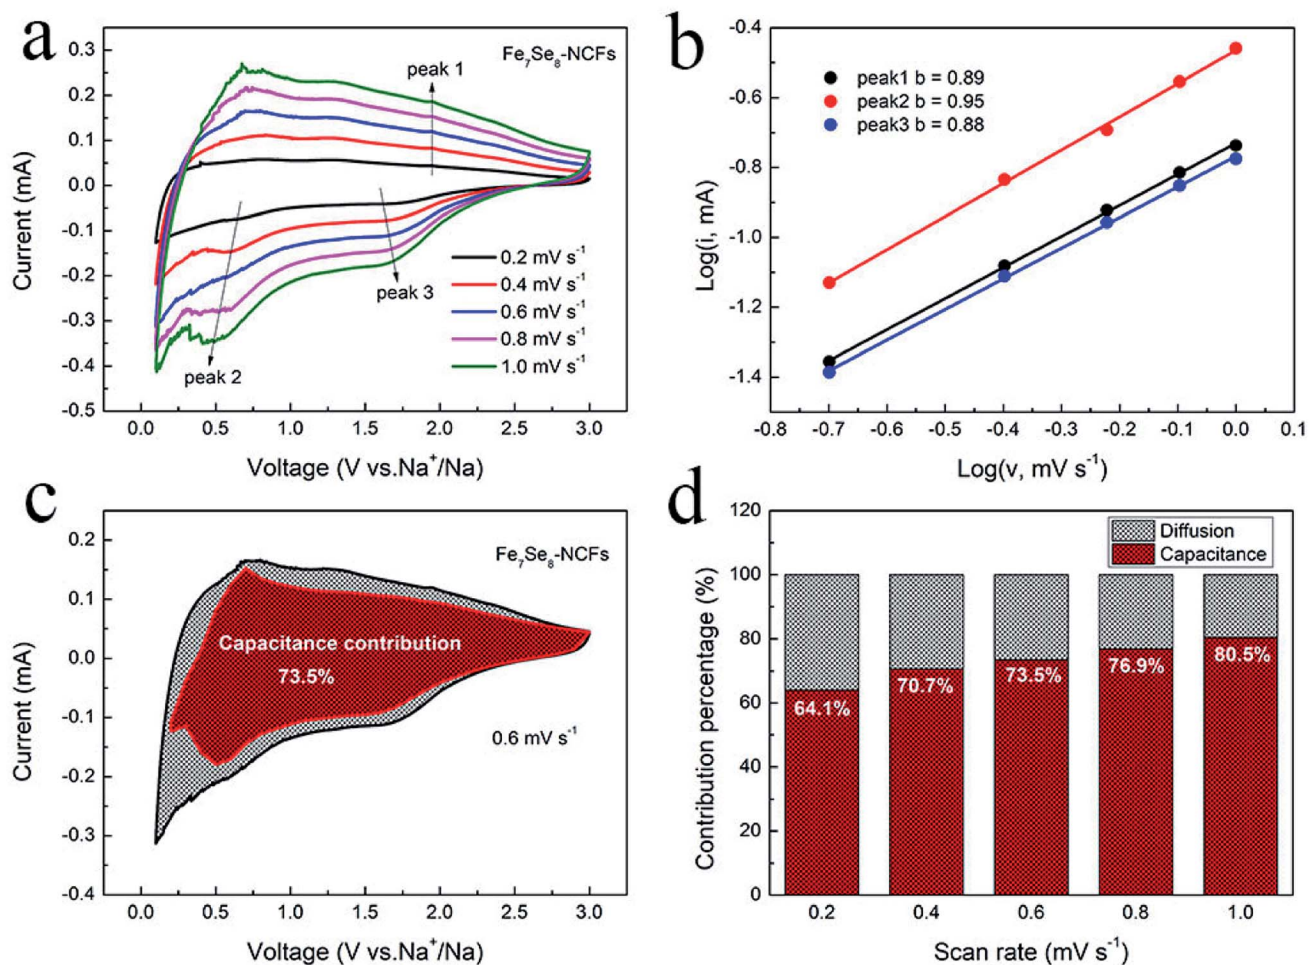


Fig. 6 Kinetics analysis of  $\text{Fe}_7\text{Se}_8\text{-NCFs}$ : (a) CV curves; (b) the corresponding  $\log(i)$  versus  $\log(v)$  plots; (c) capacitive and diffusion-controlled contribution ( $0.6 \text{ mV s}^{-1}$ ); (d) ratio of pseudocapacitive contribution.



(Fig. 6b and S7b†). All  $b$  values of  $\text{Fe}_7\text{Se}_8$ -NCFs are close to 1, which suggests mainly pseudocapacitive behavior in redox reactions. On the other hand, we calculated the ratio of pseudocapacitive contribution according to the following equation:<sup>32,33</sup>

$$i = k_1 v + k_2 v^{1/2} \quad (3)$$

$$i/v^{1/2} = k_1 v^{1/2} + k_2 \quad (4)$$

Here,  $k_1 v$  and  $k_2 v^{1/2}$  represent the capacitive contribution and ion-diffusion contribution, respectively. Fig. 6c displays the proportion of capacitive contribution of  $\text{Fe}_7\text{Se}_8$ -NCFs at  $0.6 \text{ mV s}^{-1}$  (73.5%), which is much higher than that of  $\text{Fe}_7\text{Se}_8$  (32.5%, Fig. S7c†). The incorporation of  $\text{Fe}_7\text{Se}_8$  into a 1D carbon fiber could obviously increase percentage of capacitive contributions to facilitate fast reaction kinetics for  $\text{Fe}_7\text{Se}_8$ -NCFs. In Fig. 6d, we summarized the proportion of surface pseudocapacitive contribution from  $0.2 \text{ mV s}^{-1}$  to  $1 \text{ mV s}^{-1}$ . When the sweep rate increases, the pseudocapacitive contribution of  $\text{Fe}_7\text{Se}_8$ -NCFs gradually increases, reaching as high as 80.5% at  $1 \text{ mV s}^{-1}$ . The high percentage of surface pseudocapacitive contribution is

beneficial to fast electron/ion transport kinetics to contribute to the high-rate performance of  $\text{Fe}_7\text{Se}_8$ -NCFs. EIS was conducted to analyze the change in the charge-transfer resistance ( $R_{\text{ct}}$ ) of  $\text{Fe}_7\text{Se}_8$ -NCFs before and after 100 cycles. From the fitting equivalent circuit, the  $R_{\text{ct}}$  of  $\text{Fe}_7\text{Se}_8$ -NCFs in the pristine state is  $\sim 223 \Omega$ . As the cycle number increases to 100, the  $R_{\text{ct}}$  of cycled  $\text{Fe}_7\text{Se}_8$ -NCFs decreases to  $\sim 169 \Omega$  (Fig. S8†). The decline in  $R_{\text{ct}}$  of  $\text{Fe}_7\text{Se}_8$ -NCFs after cycling could be attributed to the activation process during cycling, thus enhancing the charge transfer process and kinetics reaction.<sup>34</sup>

In view of the impressive performance of  $\text{Fe}_7\text{Se}_8$ -NCFs in half cells, a sodium ion full cell was fabricated to explore its practical feasibility. The  $\text{Fe}_7\text{Se}_8$ -NCF anode was coupled with an excessive NVP cathode to assemble the full cell. The SEM morphology, the XRD pattern and sodium storage performance of NVP are provided in Fig. S9.† The charge/discharge curves of NVP display a voltage plateau of 3.3 V in the half cell (Fig. 7a). The NVP in the half cell delivers a stable specific capacity of  $99 \text{ mA h g}^{-1}$  after 100 cycles and a favorable rate performance of  $81 \text{ mA h g}^{-1}$  at a high rate of  $2 \text{ A g}^{-1}$ , which is in good agreement with previous research.<sup>35</sup> Based on the weight of the  $\text{Fe}_7\text{Se}_8$ -NCF anode, we examined the electrochemical performance of the

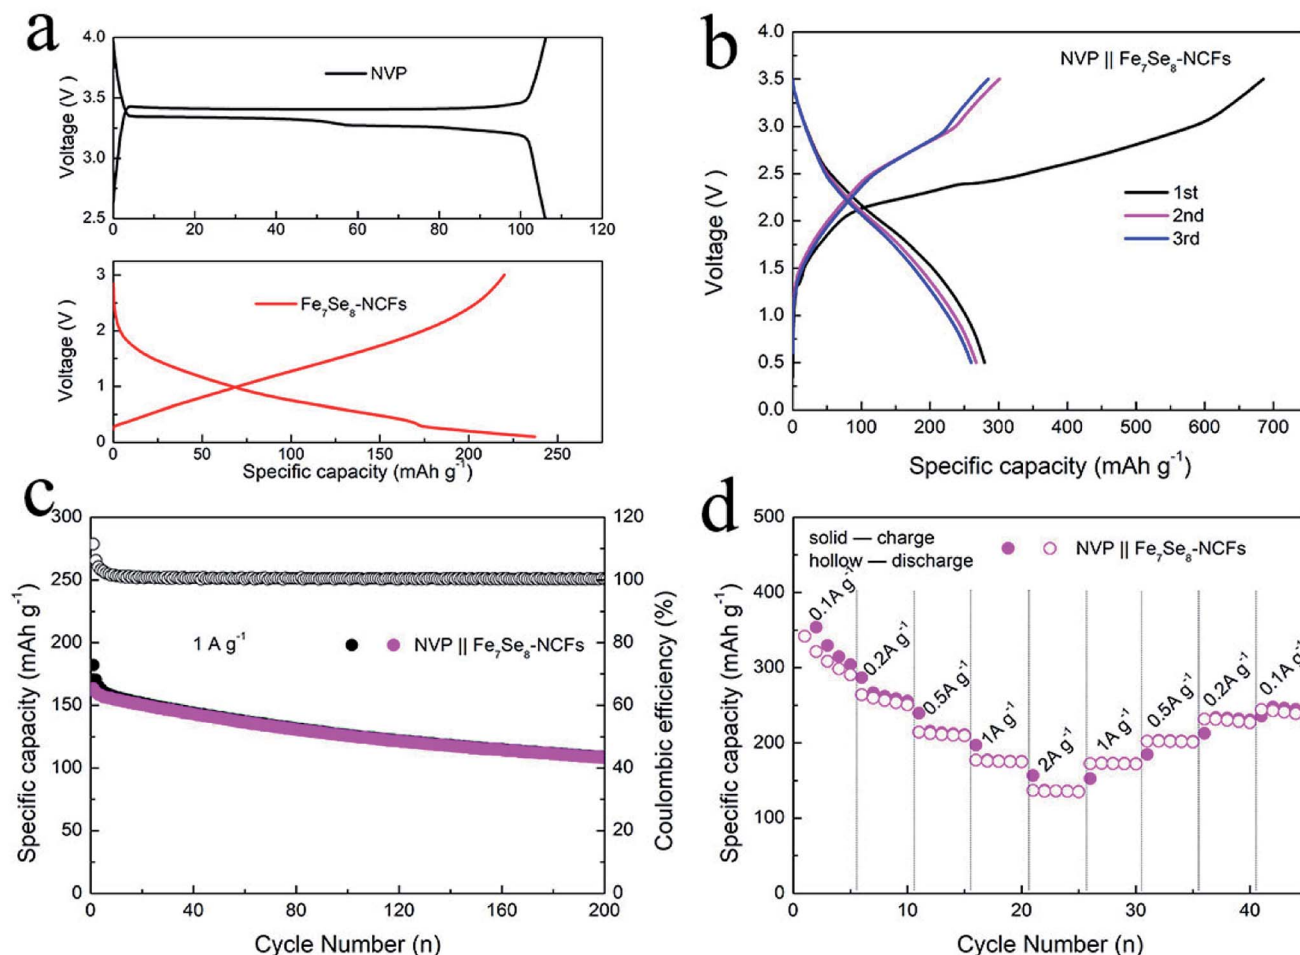


Fig. 7 (a) Charge/discharge curves of NVP and  $\text{Fe}_7\text{Se}_8$ -NCF electrodes in a half-cell. (b) Charge/discharge curves, and (c) cycling and (d) rate performance of the NVP|| $\text{Fe}_7\text{Se}_8$ -NCF full cell.



NVP||Fe<sub>7</sub>Se<sub>8</sub>-NCF sodium ion full cell. The charge/discharge curves of the NVP||Fe<sub>7</sub>Se<sub>8</sub>-NCF full cell between 0.5 and 3.5 V are obtained, which exhibits an initial charge/discharge capacity of 685/279 mA h g<sup>-1</sup> with an ICE of 40.7% (Fig. 7b). The low ICE may be attributed to the formation of a SEI film and some irreversible reactions.<sup>36</sup> The cycling and rate capability of the NVP||Fe<sub>7</sub>Se<sub>8</sub>-NCF full cell are evaluated as shown in Fig. 7c and d. The specific capacity of the full cell remains at 109 mA h g<sup>-1</sup> at 1 A g<sup>-1</sup> with a CE of ~100% after 200 cycles. Moreover, the NVP||Fe<sub>7</sub>Se<sub>8</sub>-NCF full cell exhibits favorable rate performance with a specific capacity of 136 mA h g<sup>-1</sup> at 2 A g<sup>-1</sup>. These results demonstrate the application potential of Fe<sub>7</sub>Se<sub>8</sub>-NCFs in sodium ion batteries.

## Conclusion

In conclusion, unique Fe<sub>7</sub>Se<sub>8</sub> embedded in carbon nanofibers was successfully designed for sodium storage. In consideration of the 1D carbon nanofiber network, Fe<sub>7</sub>Se<sub>8</sub>-NCFs can facilitate Na<sup>+</sup> transportation by increasing the contact area between the electrode and electrolyte to promote electrochemical reaction kinetics. Moreover, Fe<sub>7</sub>Se<sub>8</sub> encapsulated in carbon nanofibers, the Fe<sub>7</sub>Se<sub>8</sub>-NCF electrode, can effectively accommodate the volume change to keep the structural integrity of Fe<sub>7</sub>Se<sub>8</sub>-NCFs during a conversion reaction process. Hence, the Fe<sub>7</sub>Se<sub>8</sub>-NCF electrode shows remarkable stability (223 mA h g<sup>-1</sup> at 0.1 A g<sup>-1</sup>, after 400 cycles) and improved rate capability (153 mA h g<sup>-1</sup>, 2 A g<sup>-1</sup>) in half-cells. Impressively, when coupled with NVP to assemble a full cell, the NVP||Fe<sub>7</sub>Se<sub>8</sub>-NCF full cell exhibits its practical feasibility with a specific capacity of 109 mA h g<sup>-1</sup> after 200 cycles (1 A g<sup>-1</sup>) and a favorable rate capability of 136 mA h g<sup>-1</sup> at a high rate of 2 A g<sup>-1</sup>.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was financially supported by the Natural Science Foundation of Guangdong Province (2018A030313739) and Science and Technology Program of Guangzhou (No. 2019050001).

## References

- Y. Jiang, D. Song, J. Wu, Z. Wang, S. Huang, Y. Xu, Z. Chen, B. Zhao and J. Zhang, Sandwich-like SnS<sub>2</sub>/graphene/SnS<sub>2</sub> with expanded interlayer distance as high-rate lithium/sodium-ion battery anode materials, *ACS Nano*, 2019, **13**, 9100–9111.
- L. Fu, Z. Bi, B. Wei, L. Huang, X. Zhang, Z. Chen, H. Liao, M. Li, C. Shang and X. Wang, Flower-like Cu<sub>2</sub>SnS<sub>3</sub> Nanostructure Materials with High Crystallinity for Sodium Storage, *Nanomaterials*, 2018, **8**, 475.
- S. Wang, L. Xia, L. Yu, L. Zhang, H. Wang and X. W. D. Lou, Free-Standing Nitrogen-Doped Carbon Nanofiber Films: Integrated Electrodes for Sodium-Ion Batteries with Ultralong Cycle Life and Superior Rate Capability, *Adv. Energy Mater.*, 2016, **6**, 1502217.
- Y. Fang, B. Y. Guan, D. Luan and X. W. D. Lou, Synthesis of CuS@CoS<sub>2</sub> Double-Shelled Nanoboxes with Enhanced Sodium Storage Properties, *Angew. Chem., Int. Ed.*, 2019, **58**, 7739–7743.
- C. Guo, W. Zhang, Y. Liu, J. He, S. Yang, M. Liu, Q. Wang and Z. Guo, Constructing CoO/Co<sub>3</sub>S<sub>4</sub> Heterostructures Embedded in N-doped Carbon Frameworks for High Performance Sodium-Ion Batteries, *Adv. Funct. Mater.*, 2019, **29**, 1901925.
- Z. Hu, Q. Liu, W. Lai, Q. Gu, L. Li, M. Chen, W. Wang, S. L. Chou, Y. Liu and S. X. Dou, Manipulating Molecular Structure and Morphology to Invoke High-Performance Sodium Storage of Copper Phosphide, *Adv. Energy Mater.*, 2020, **10**, 1903542.
- X. Li, M. Sun, J. Ni and L. Li, Template-Free Construction of Self-Supported Sb Prisms with Stable Sodium Storage, *Adv. Energy Mater.*, 2019, **9**, 1901096.
- L. Fu, X. Zheng, L. Huang, C. Shang, K. Lu, X. Zhang, B. Wei and X. Wang, Synthesis and Investigation of CuGeO<sub>3</sub> Nanowires as Anode Materials for Advanced Sodium-Ion Batteries, *Nanoscale Res. Lett.*, 2018, **13**, 193.
- H. Li, K. Wang, M. Zhou, W. Li, H. Tao, R. Wang, S. Cheng and K. Jiang, Facile Tailoring of Multidimensional Sb for Sodium Storage Applications, *ACS Nano*, 2019, **13**, 9533–9540.
- Y. Wang, Y. Wang, Y. X. Wang, X. Feng, W. Chen, J. Qian, X. Ai, H. Yang and Y. Cao, *In Situ* Formation of Co<sub>9</sub>S<sub>8</sub> Nanoclusters in Sulfur-Doped Carbon Foam as a Sustainable and High-Rate Sodium-Ion Anode, *ACS Appl. Mater. Interfaces*, 2019, **11**, 19218–19226.
- K. Zhang, Z. Hu, X. Liu, Z. Tao and J. Chen, FeSe<sub>2</sub> Microspheres as a High-Performance Anode Material for Na-Ion Batteries, *Adv. Mater.*, 2015, **27**, 3305–3309.
- D. M. Zhang, J. H. Jia, C. C. Yang and Q. Jiang, Fe<sub>7</sub>Se<sub>8</sub> nanoparticles anchored on N-doped carbon nanofibers as high-rate anode for sodium-ion batteries, *Energy Storage Materials*, 2020, **24**, 439–449.
- J. Xia, L. Liu, S. Jamil, J. Xie, H. Yan, Y. Yuan, Y. Zhang, S. Nie, J. Pan, X. Wang and G. Cao, Free-standing SnS/C nanofiber anodes for ultralong cycle-life lithium-ion batteries and sodium-ion batteries, *Energy Storage Materials*, 2019, **17**, 1–11.
- Z. Sun, X. Wu, Z. Gu, P. Han, B. Zhao, D. Qu, L. Gao, Z. Liu, D. Han and L. Niu, Rationally designed nitrogen-doped yolk-shell Fe<sub>7</sub>Se<sub>8</sub>/carbon nanoboxes with enhanced sodium storage in half/full cells, *Carbon*, 2020, **166**, 175–182.
- J. Xia, Y. Yuan, H. Yan, J. Liu, Y. Zhang, L. Liu, S. Zhang, W. Li, X. Yang, H. Shu, X. Wang and G. Cao, Electrospun SnSe/C nanofibers as binder-free anode for lithium-ion and sodium-ion batteries, *J. Power Sources*, 2020, **449**, 227559.
- C. Shang, S. Dong, S. Zhang, P. Hu, C. Zhang and G. Cui, A Ni<sub>3</sub>S<sub>2</sub>-PEDOT monolithic electrode for sodium batteries, *Electrochem. Commun.*, 2015, **50**, 24–27.





- 17 J. Zhang, Y. Liu, H. Liu, Y. Song, S. Sun, Q. Li, X. Xing and J. Chen, Urchin-Like  $\text{Fe}_3\text{Se}_4$  Hierarchitectures: A Novel Pseudocapacitive Sodium-Ion Storage Anode with Prominent Rate and Cycling Properties, *Small*, 2020, **16**, 2000504.
- 18 J. Li, J. Zhao, R. Tang, Q. Chen, Z. Niu, M. Li, C. Guo, J. Su and L. Zhang, Facilely fabricating FeSe nanoparticles embedded in N-doped carbon towards promoting sodium storage behaviors, *J. Power Sources*, 2020, **449**, 227517.
- 19 X. Hu, Y. Liu, J. Li, G. Wang, J. Chen, G. Zhong, H. Zhan and Z. Wen, Self-Assembling of Conductive Interlayer-Expanded  $\text{WS}_2$  Nanosheets into 3D Hollow Hierarchical Microflower Bud Hybrids for Fast and Stable Sodium Storage, *Adv. Funct. Mater.*, 2019, **30**, 1907677.
- 20 L. Hu, L. He, X. Wang, C. Shang and G. Zhou, MnSe embedded in carbon nanofibers as advanced anode material for sodium ion batteries, *Nanotechnology*, 2020, **31**, 335402.
- 21 T. Liu, Y. Li, L. Zhao, F. Zheng, Y. Guo, Y. Li, Q. Pan, Y. Liu, J. Hu and C. Yang, *In Situ* Fabrication of Carbon-Encapsulated  $\text{Fe}_7\text{X}_8$  ( $\text{X} = \text{S}, \text{Se}$ ) for Enhanced Sodium Storage, *ACS Appl. Mater. Interfaces*, 2019, **11**, 19040–19047.
- 22 Z. Man, P. Li, D. Zhou, Y. Wang, X. Liang, R. Zang, P. Li, Y. Zuo, Y. M. Lam and G. Wang, Two Birds with One Stone:  $\text{FeS}_2@\text{C}$  Yolk-Shell Composite for High-Performance Sodium-Ion Energy Storage and Electromagnetic Wave Absorption, *Nano Lett.*, 2020, **20**, 3769–3777.
- 23 Y. He, M. Luo, C. Dong, X. Ding, C. Yin, A. Nie, Y. Chen, Y. Qian and L. Xu, Coral-like  $\text{Ni}_x\text{Co}_{1-x}\text{Se}_2$  for Na-ion battery with ultralong cycle life and ultrahigh rate capability, *J. Mater. Chem. A*, 2019, **7**, 3933–3940.
- 24 H. Yang, R. Xu, Y. Yao, S. Ye, X. Zhou and Y. Yu, Multicore-Shell Bi@N-doped Carbon Nanospheres for High Power Density and Long Cycle Life Sodium-and Potassium-Ion Anodes, *Adv. Funct. Mater.*, 2019, **29**, 1809195.
- 25 M. Wan, R. Zeng, K. Chen, G. Liu, W. Chen, L. Wang, N. Zhang, L. Xue, W. Zhang and Y. Huang,  $\text{Fe}_7\text{Se}_8$  nanoparticles encapsulated by nitrogen-doped carbon with high sodium storage performance and evolving redox reactions, *Energy Storage Materials*, 2018, **10**, 114–121.
- 26 H. Wu, X. Chen, C. Qian, H. Yan, C. Yan, N. Xu, Y. Piao, G. Diao and M. Chen, Confinement Growth of Layered  $\text{WS}_2$  in Hollow Beaded Carbon Nanofibers with Synergistic Anchoring Effect to Reinforce  $\text{Li}^+/\text{Na}^+$  Storage Performance, *Small*, 2020, **16**, 2000695.
- 27 Z. Li, Y. Fang, J. Zhang and X. W. D. Lou, Necklace-Like Structures Composed of  $\text{Fe}_3\text{N}@\text{C}$  Yolk-Shell Particles as an Advanced Anode for Sodium-Ion Batteries, *Adv. Mater.*, 2018, **30**, 1800525.
- 28 M. Yousaf, Y. Wang, Y. Chen, Z. Wang, A. Firdous, Z. Ali, N. Mahmood, R. Zou, S. Guo and R. P. S. Han, A 3D Trilayered CNT/ $\text{MoSe}_2$ /C Heterostructure with an Expanded  $\text{MoSe}_2$  Interlayer Spacing for an Efficient Sodium Storage, *Adv. Energy Mater.*, 2019, **9**, 1900567.
- 29 W. Tian, W. Ma, Z. Feng, F. Tian, H. Li, J. Liu and S. Xiong, Formation of hierarchical  $\text{Fe}_7\text{Se}_8$  nanorod bundles with enhanced sodium storage properties, *J. Energy Chem.*, 2020, **44**, 97–105.
- 30 L. Hu, C. Shang, L. Huang, X. Wang and G. Zhou,  $\text{Cu}_3\text{Ge}$  coated by nitrogen-doped carbon nanorods as advanced sodium-ion battery anodes, *Ionics*, 2019, **26**, 719–726.
- 31 C. C. Li, B. Wang, D. Chen, L. Y. Gan, Y. Feng, Y. Zhang, Y. Yang, H. Geng, X. Rui and Y. Yu, Topotactic Transformation Synthesis of 2D Ultrathin  $\text{GeS}_2$  Nanosheets toward High-Rate and High-Energy-Density Sodium-Ion Half/Full Batteries, *ACS Nano*, 2020, **14**, 531–540.
- 32 P. Liu, J. Han, K. Zhu, Z. Dong and L. Jiao, Heterostructure  $\text{SnSe}_2/\text{ZnSe}@ \text{PDA}$  Nanobox for Stable and Highly Efficient Sodium-Ion Storage, *Adv. Energy Mater.*, 2020, **10**, 2000741.
- 33 J. Wang, B. Wang, X. Liu, J. Bai, H. Wang and G. Wang, Prussian blue analogs (PBA) derived porous bimetal (Mn, Fe) selenide with carbon nanotubes as anode materials for sodium and potassium ion batteries, *Chem. Eng. J.*, 2020, **382**, 123050.
- 34 X. Wang, X. Li, Q. Li, H. Li, J. Xu, H. Wang, G. Zhao, L. Lu, X. Lin, H. Li and S. Li, Improved Electrochemical Performance Based on Nanostructured  $\text{SnS}_2@\text{CoS}_2\text{-rGO}$  Composite Anode for Sodium-Ion Batteries, *Nano-Micro Lett.*, 2018, **10**, 46.
- 35 S. Shi, C. Sun, X. Yin, L. Shen, Q. Shi, K. Zhao, Y. Zhao and J. Zhang, FeP Quantum Dots Confined in Carbon-Nanotube-Grafted P-Doped Carbon Octahedra for High-Rate Sodium Storage and Full-Cell Applications, *Adv. Funct. Mater.*, 2020, **30**, 1909283.
- 36 Z. Ali, M. Asif, X. Huang, T. Tang and Y. Hou, Hierarchically Porous  $\text{Fe}_2\text{CoSe}_4$  Binary-Metal Selenide for Extraordinary Rate Performance and Durable Anode of Sodium-Ion Batteries, *Adv. Mater.*, 2018, 1802745.

